

This file is part of the following work:

New, Brian T.E. (2006) *Controls of copper and gold distribution in the Kucing Liar deposit, Ertsberg mining district, West Papua, Indonesia*. PhD Thesis, James Cook University.

Access to this file is available from:

<https://doi.org/10.25903/v1te%2D1q86>

Copyright © 2006 Brian T.E. New

The author has certified to JCU that they have made a reasonable effort to gain permission and acknowledge the owners of any third party copyright material included in this document. If you believe that this is not the case, please email

researchonline@jcu.edu.au

Controls of copper and gold distribution in the Kucing Liar deposit, Ertsberg Mining District, West Papua, Indonesia

B.T.E. New


Thesis submitted by Brian New *BSc(Hon.)* November 2006
For the degree of Doctor of Philosophy (*PhD.*),
School of Earth Sciences, James Cook University, Australia

Tembagapura



The “copper town” of Tembagapura is built on glacial sediments in a deeply incised valley. The town receives 8m of rain per year on average. The smaller barracks of Hidden Valley is visible at upper right and is where drill core was housed.

Mt Zaagkham

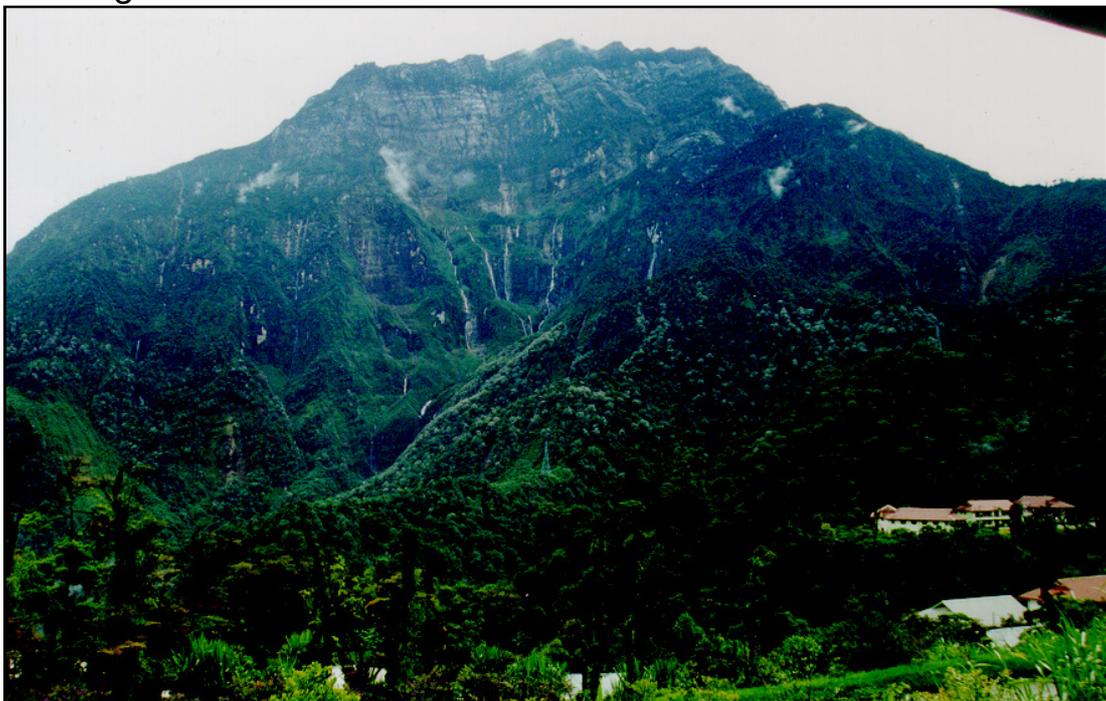

Mt Zaagkham as viewed from the core shed where drill core samples were investigated. This very impressive mountain is generally only visible in the morning before cloud cover and accompanying rain sets in for the afternoon.

Statement of Access

I, the undersigned, the author of this thesis, understand that James Cook University will make it available for use within the university library and, by microfilm or other means, allow access to users of other approved libraries.

All users consulting this thesis by either hardcopy or digital means will have to sign the following statement:

“In consulting this thesis I agree not to copy or closely paraphrase it in whole or in part without the written consent of the author; and to make proper public written knowledge for any assistance which I have obtained from it”

The assay data made available for every drill hole in the Kucing Liar resource delineation by PT Freeport Indonesia for this research and the results of their analysis are included. However, due to the economic sensitivity of the project, the full data set is not included in this volume.

Beyond this I do not wish to place any restriction on access to this thesis.

Brian New

November 2006

Declaration

I declare that this thesis is my own work and has not been submitted in any form for another degree or diploma at any other university or institution of tertiary education. Where analytical work has been completed by others they have been acknowledged. Information derived from the published or unpublished work of other has been acknowledged in the text and a list of these references is supplied.

Brian New

November 2006

Acknowledgements

This research topic was originally conceived by Roger Taylor and Peter Pollard (James Cook University) and was initiated by Chuck Brannon for PT Freeport Indonesia. Steve van Nort and George Macdonald of PT Freeport Indonesia provided continued support. The company supplied transport, accommodation and provisions for multiple field visits to the mine site in addition to funds for all analytical requirements and a living allowance for a three year period. This generous financial assistance to research is gratefully recognized. Staff at the mine site who have assisted this research by way of many discussions include Peter Manning, Nur Wiwoho and Sugeng Widodo as well as Bowo Kusnanto and Noris del bel Belluz. Detailed regional and local map material was kindly provided by Keith Parris. Uttu Mekiel and Aris Sitohang continuously provided logistical assistance for drill core examination.

The (numerous) drafts, commonly unfinished, and final manuscript were assessed by Pat Williams and his assistance in thesis compilation was much appreciated. Additional comments and suggestions for improvements were also provided by Roger Taylor and Peter Pollard. I would like to thank Roger and Peter for their invaluable teaching and friendship. I would also like to extend thanks to long-standing staff of the School, Mike Rubenach, Bob Henderson, Tim Bell and more recently Pat Williams, Nick Oliver and Tim Baker for the enjoyable education I have received over the many years I have spent at JCU. Darren Mylrea, Sharon Ness and Kevin Blake from the Advanced Analytical Centre at JCU provided much appreciated analytical support for sample preparation for geochronology and isotope analysis as well as XRD and SEM analyses and interpretations.

Finally I would like to thank my family for continued support and all the friends I have accumulated while studying at JCU from 1988-2006.

Mineral Abbreviations

Ah	Anhydrite
Bn	Bornite
Bt	Biotite
Bp	Brown phlogopite
Cc	Calcite
Cp	Chalcopyrite
Cpx	Clinopyroxene
Cspy	Coarse pyrite
Ct	Chalcocite
Cv	Covellite
Cy	Chrysotile
Dg	Digenite
Do	Dolomite
En	Enargite
Fnpy	Fine pyrite
Fo	Forsterite
Gl	Galena
Gp	Green phlogopite
Gt	Garnet
Hb	Hornblende
Hu	Humite
Kf	K-feldspar
Mo	Molybdenite
Ms	Muscovite
Mt	Magnetite
Nk	Nukundamite
Pl	Plagioclase
Po	Pyrrhotite
Py	Pyrite
Qz	Quartz
Se	Serpentine
Tl	Talc
Tr	Tremolite-actinolite
Sp	Sphalerite

Table of Contents

1. INTRODUCTION

1.1	<i>Regional and local setting</i>	5
1.1.1	Geology of New Guinea and the Southern Central Ranges	5
	Tectonic evolution of New Guinea	6
	Stratigraphy and structure of the Southern Central Ranges	9
1.1.2	Geology of the Ertsberg Mining District	12
1.2	<i>Access and methods</i>	15
1.2.1	Physiography of the mining district	15
1.2.2	Sources of data	18

2. HOST ROCKS

2.1	<i>Previous work and sources of data</i>	24
2.1.1	Regional stratigraphic sequence	24
2.1.2	District outcrop and deep drilling	27
2.2	<i>Results</i>	31
2.2.1	Descriptions of local unaltered lithological sequences	32
2.2.2	Textures developed in low-intensity distal alteration	40

3. PARAGENESIS

3.1	<i>Mineral textures, assemblages and timing relationships</i>	48
	Group I paragenesis	48
	Group II	58
	Group III	62
	Group IV	66
	Intrusive rocks	72
3.2	<i>Interpretation of Kucing Liar paragenesis</i>	74
	Classification and inter-relationships of Kucing Liar mineral assemblages	74
	Petrologically defined conditions of the Kucing Liar hydrothermal system	80

4. STRUCTURAL SETTING AND FLUID FLOW

4.1	<i>Stratigraphic and fluid flow modelling</i>	83
4.1.1	Lithological distribution	83
	Stratigraphic sequence recognition	83
	Large-scale geometry	89
4.1.2	Hydrothermal mineral distribution	95
	Patterns of hydrothermal alteration	95
	Large-scale mineral distributions	99
4.2	<i>Large-scale controls on fluid infiltration</i>	106
4.2.1	Structural geometry of Kucing Liar alteration	106
4.2.2	Driving forces of fluid flow	108

Table of Contents (cont.)

5. ORE MINERAL DISTRIBUTION AND METAL ZONING

5.1	<i>Mineralisation populations and spatial distributions</i>	111
5.1.1	Spatial models of ore mineral and metal distributions	111
	Metal distributions relative to the structural setting	111
	Elevation patterns of metals and ore minerals	127
5.1.2	Inter-element associations	131
	Copper-gold relationships	133
	Trace metal relationships	138
5.2	<i>Interpretation of metal assay data</i>	143
5.2.1	Defining the mineralisation process through metal associations	143
	Styles of mineralisation	143
	Zoning patterns	144
5.2.2	Metal complexes and ore precipitation	145

6. FLUID INCLUSION STUDIES

6.1	<i>Fluid inclusion petrography</i>	149
6.1.1	Sample location and descriptions	149
6.1.2	Occurrence and paragenesis	154
6.2	<i>Thermometric experiments</i>	159
6.2.1	Results of freezing and heating	159
	Solid phase melting temperatures	160
	Vapour homogenisation	163
6.2.2	Determination of fluid composition	167
	Salt system	167
	Salinity calculations	168
6.3	<i>Interpretation of fluid inclusion data</i>	170
6.3.1	Fluid populations	170
6.3.2	Fluid phase development	171

7. STABLE ISOTOPE GEOCHEMISTRY

7.1	<i>Isotopic analyses</i>	176
7.1.1	Results of analyses	176
7.1.2	Fluid compositions	181
	Results of fractionation calculations	187
7.2	<i>Interpretation</i>	189
	Fluid reservoirs and isotopic compositions	189
	Magmatic exsolution processes	192

Table of Contents (cont.)**8. $^{40}\text{Ar}/^{39}\text{Ar}$ AND RE-OS GEOCHRONOLOGY**

8.1	<i>Sample collection</i>	195
8.2	<i>Age spectra and results from analyses</i>	199
8.3	<i>Interpretation of age data</i>	208
	Interpretation of Kucing Liar age data	208
	Geochronology of the Ertzberg Mining District	209

9. DISCUSSION

9.1	<i>Tectonic-magmatic setting of fluid infiltration</i>	214
9.1.1	Tectonic transition and porphyry emplacement	214
9.1.2	Progressive deformation and structural geometry	217
9.2	<i>Fluid evolution leading to hydrothermal mineralization</i>	223
9.2.1	The collapse of magmatic-hydrothermal systems	223
9.2.2	Effect of fluid mixing on ore chemistry	224
9.3	<i>Kucing Liar in the continuum of porphyry-related ore systems</i>	227
9.3.1	Classification of porphyry-epithermal ores	227
9.3.2	Juxtaposition of porphyry-epithermal systems	230
9.4	<i>Concluding remarks</i>	233

List of Figures

<i>Figure 1-1 Distribution of porphyry Cu±Mo±Au deposits in the circum-Pacific region</i>	1
<i>Figure 1-2 Ore deposit environments related to porphyritic intrusions</i>	2
<i>Figure 1-3 Location of the Ertsberg Mining District</i>	3
<i>Figure 1-4 Physiography of Irian Jaya and Papua New Guinea</i>	5
<i>Figure 1-5 Palimpsestic reconstruction of the evolution of New Guinea</i>	7
<i>Figure 1-6 Tectonics and igneous intrusions of New Guinea (reproduced from McDowell et al., 1996)</i>	8
<i>Figure 1-7 Sedimentary record of the Timika-Tembagapura region (reproduced from Parris, 1994a).</i>	10
<i>Figure 1-8 Geology of southern flanks of the Central Range</i>	11
<i>Figure 1-9 Geological map of the Ertsberg Mining District (supplied by PT Freeport Indonesia)</i>	14
<i>Figure 1-10 Physiography of the Southern Ranges and Ertsberg Mining District</i>	16
<i>Figure 1-11 Position of Kucing Liar mineralisation relative to Grasberg Igneous Complex</i>	19
<i>Figure 1-12 Plan view of all Kucing Liar drill traces logged for this research program</i>	20
<i>Figure 1-13 Layout of all holes in each drill station logged for this research program</i>	21
<i>Figure 2-1 Plan projection showing collar locations for stratigraphical drillholes</i>	30
<i>Figure 2-2 Lithology and composition of unmineralised stratigraphy</i>	31
<i>Figure 3-1 Example of GADDS X-ray diffraction identification of hornfels alteration in shale</i>	50
<i>Figure 3-2 Composition of clinopyroxene and feldspar</i>	51
<i>Figure 3-3 Composition of garnet</i>	52
<i>Figure 3-4 Example of GADDS X-ray diffraction identification of a humite group mineral</i>	55
<i>Figure 4-1 Stratigraphic patterns identified in drilling</i>	88
<i>Figure 4-2 Serial sections of Kucing Liar lithology (refer Chapter 1 for section locations)</i>	90
<i>Figure 4-3 Interpretative cross sections of Kucing Liar stratigraphy from wireframes</i>	92
<i>Figure 4-4 Interpretative plan sections of Kucing Liar stratigraphy from wireframes</i>	93
<i>Figure 4-5 Interpretative longitudinal sections of Kucing Liar stratigraphy from wireframes</i>	94
<i>Figure 4-6 Lithological patterns and mineral abundances in representative drill holes</i>	96
<i>Figure 4-7 Distribution of calcite, clinopyroxene, garnet, humite and phlogopite</i>	101
<i>Figure 4-8 Distribution of dominant K-feldspar + biotite alteration</i>	102
<i>Figure 4-9 Distribution of extensive magnetite and tremolite-actinolite alteration</i>	103
<i>Figure 4-10 Distribution of rocks dominated by quartz, muscovite and anhydrite alteration</i>	104
<i>Figure 4-11 Distribution of ore sulphides, pyrite, chalcopyrite and covellite</i>	105
<i>Figure 5-1 Downhole distribution of metal concentrations</i>	113
<i>Figure 5-2 Spatial distribution and structural controls of pyrite alteration</i>	117
<i>Figure 5-3 Spatial distribution and structural controls of chalcopyrite</i>	118
<i>Figure 5-4 Spatial distribution and structural controls of covellite</i>	119
<i>Figure 5-5 Spatial distribution and structural controls of copper</i>	120
<i>Figure 5-6 Spatial distribution and structural controls of zinc</i>	121
<i>Figure 5-7 Spatial distribution and structural controls of lead</i>	122
<i>Figure 5-8 Spatial distribution and structural controls of gold</i>	123
<i>Figure 5-9 Spatial distribution and structural controls of silver</i>	124
<i>Figure 5-10 Spatial distribution and structural controls of arsenic</i>	125
<i>Figure 5-11 Spatial distribution and structural controls of antimony</i>	126
<i>Figure 5-12 Variation of average copper and gold grades relative to elevation</i>	127
<i>Figure 5-13 Elevation variations of Ag-Zn-Pb and As-Sb relative to Cu-Au</i>	128
<i>Figure 5-14 Characteristics of chalcopyrite and covellite-bearing ore relative to elevation</i>	129
<i>Figure 5-15 Distribution of copper, gold and sulphur phases relative to elevation</i>	130
<i>Figure 5-16 Global relationship of copper and gold</i>	132
<i>Figure 5-17 Copper and gold distributions in assay populations classified by logged copper sulphide species</i>	134
<i>Figure 5-18 Cu-Au grades of assay intervals dominated by various paragenetic associations</i>	135
<i>Figure 5-19 Copper and gold grade distributions in populations classified by dominant paragenetic stage in assay interval</i>	136
<i>Figure 5-20 Minor element variations with respect to copper</i>	139

List of Figures (cont.)

Figure 5-21 Minor element variations of the low-Cu ore sample population with respect to gold	140
Figure 5-22 Correlation coefficients for significant sample populations in Kucing Liar	142
Figure 5-23 Zoning of ore sulphides, pyrite, chalcopyrite and covellite and Cu-Au-As	147
Figure 6-1 Location of fluid inclusion samples	151
Figure 6-2 First melt (eutectic) and final melting temperatures of ice in frozen inclusions	161
Figure 6-3 Final melting temperatures of halite and sylvite in fluid inclusions	162
Figure 6-4 Final homogenisation temperature versus ice melting temperatures	164
Figure 6-5 Vapour homogenisation versus salt melting temperatures in SLV-type inclusions	166
Figure 6-6 Final homogenisation temperatures of fluid inclusions	166
Figure 6-7 Homogenisation temperature versus calculated salinities of fluid inclusions	169
Figure 6-8 Homogenisation temperatures of fluid inclusions	173
Figure 6-9 Bulk salinity of magmatic fluids exsolved from water saturated magmas	174
Figure 6-10 Phase separation of critical magmatic fluid (from Meinert, 1998)	174
Figure 7-1 Histograms showing analysed oxygen, hydrogen and sulphur isotope ratios	180
Figure 7-2 Fractionation curves for oxygen (a-d), hydrogen (e) and sulphur (f)	185
Figure 7-3 Histograms showing calculated oxygen, hydrogen and sulphur isotope ratios	188
Figure 7-4 Calculated $\delta^{18}\text{O}_{\text{FLUID}}$ for the Kucing Liar paragenesis	191
Figure 7-5 Calculated Hydrogen and oxygen isotope compositions of Kucing Liar fluids	193
Figure 8-1 Grainsize of muscovite crystals	197
Figure 8-2 Photographs of geochronology samples	198
Figure 8-3 Age spectra and isochron plots of sample KL28-1 360.3m (green phlogopite)	200
Figure 8-4 Age spectra and isochron plots of sample KL32-8 331.0m (green phlogopite)	201
Figure 8-5 Age spectra and isochron plots of sample KL32-5 539.6m (brown biotite)	202
Figure 8-6 Age spectra and isochron plots of sample KL32-5 652.4m (brown biotite)	203
Figure 8-7 Age spectra and isochron plots of sample KL32-5 465.3m (brown biotite)	204
Figure 8-8 Age spectra and isochron plots of sample KL32-8 455.9m (muscovite)	205
Figure 8-9 Age spectra and isochron plots of sample KL32-1 255.7m (muscovite)	206
Figure 8-10 Absolute ages of hydrothermal minerals and their accuracies	207
Figure 8-11 Geochronology of the Ertsberg Mining District	211
Figure 9-1 Analogue model of deformation front for various convergence angles	216
Figure 9-2 Geometry and structural detail of fault jogs	220
Figure 9-3 Naming convention for structures present in a left lateral fault-slip system	220
Figure 9-4 Geometric characteristics of strike-slip faults	221
Figure 9-5 Speculative models for development of structural offset in Idenberg Fault Zone	222
Figure 9-6 Generalised model of porphyry-related ore systems	229
Figure 9-7 Plot of $\log f_{\text{S}_2}$ – Temperature for fluids in porphyry systems	230
Figure 9-8 Telescoping of epithermal systems into porphyry environment	232

List of Plates

<i>Plate 1-1 Relief of the Ertzberg Mining District and access routes</i>	17
<i>Plate 2-1 Large-scale exposure of host stratigraphy</i>	28
<i>Plate 2-2 Examples of Ekmai Sandstone and limestone</i>	33
<i>Plate 2-3 Outcrop of the Waripi Limestone</i>	34
<i>Plate 2-4 Examples of Waripi Limestone visible textures</i>	36
<i>Plate 2-5 Examples of Faumai Limestone visible and micro-textures</i>	38
<i>Plate 2-6 Example of Sirga Sandstone</i>	39
<i>Plate 2-7 Example of Kais Limestone</i>	39
<i>Plate 2-8 Examples of dolomitisation textures</i>	41
<i>Plate 2-9 Examples of dolomitisation micro-textures in peloid limestone</i>	42
<i>Plate 2-10 Examples of dolomitisation micro-textures in foraminiferal limestone</i>	43
<i>Plate 2-11 Examples of distal hydrothermal alteration</i>	45
<i>Plate 2-12 An axample of hydrothermal micro-textures in sandstone</i>	46
<i>Plate 3-1 Textures and timing relationships of anhydrous Group I minerals</i>	53
<i>Plate 3-2 Textures and timing relationships of hydrous Group I minerals</i>	57
<i>Plate 3-3 Textures and relative timing of potassic Group II minerals</i>	60
<i>Plate 3-4 Textures and relative timing of non-potassic Group II minerals</i>	62
<i>Plate 3-5 Textures and timing relationships of Group III minerals</i>	65
<i>Plate 3-6 Textures and timing relationships of pyrite, pyrrhotite and chalcopyrite</i>	68
<i>Plate 3-7 Textures and relative timing of covellite, enargite and nukundamite</i>	70
<i>Plate 3-8 Textures and timing relationships of galena, sphalerite and molybdenite</i>	71
<i>Plate 3-9 Visible and microscopic textures of common alteration effects in monzonite</i>	73
<i>Plate 3-10 Visible and microscopic textures of diorite</i>	73
<i>Plate 4-1 An example of lithological sequence commonly found in faulted regions</i>	87
<i>Plate 6-1 Photographs of wafers and blocks of fluid inclusion samples</i>	152
<i>Plate 6-2 Photomicrographs of textural settings of crystals that host fluid inclusions</i>	153
<i>Plate 6-3 Fluid inclusion types in quartz</i>	156
<i>Plate 6-4 Fluid inclusion occurrences in quartz</i>	156
<i>Plate 6-5 Examples of fluid inclusion trails</i>	157
<i>Plate 6-6 Crosscutting fluid inclusion relationships</i>	158

List of Tables

<i>Table 1-1 Copper and/or gold resources of the Ertsberg Mining District</i>	4
<i>Table 2-1 Descriptions of stratigraphy in the Ertsberg Mining District</i>	26
<i>Table 5-1 Average grade of mineralisation in different mineral associations</i>	135
<i>Table 5-2 Average metal concentrations in assay intervals classified by copper species present</i>	141
<i>Table 6-1 First melt temperatures of selected water-salt systems</i>	167
<i>Table 7-1 Stable isotope samples and results (‰)</i>	178
<i>Table 7-2 Temperatures used for calculating fluid isotope compositions</i>	182
<i>Table 7-3 Mineral-H₂O fractionation equations for oxygen (Temperature (T) is in Kelvin)</i>	183
<i>Table 7-4 Mineral-H₂O fractionation equations for hydrogen (Temperature (T) is in Kelvin)</i>	184
<i>Table 7-5 Mineral-SO₄/H₂S fractionation equations for sulphur (Temperature (T) is in Kelvin)</i>	184
<i>Table 8-1 Ages and precisions for ⁴⁰Ar/³⁹Ar methods on selected minerals</i>	207
<i>Table 8-2 Geochronology of Ertsberg Mining District hydrothermal minerals</i>	211
<i>Table 8-3 Geochronology of Ertsberg Mining District intrusions</i>	212

Abstract

Kucing Liar is a large sediment-hosted Cu-Au mineralized system containing some 15Moz of gold and 5Mt of copper in ~500Mt of ore. It is situated in the Ertzberg Mining District in the Central Ranges of New Guinea, in the Indonesian province of West Papua. This study demonstrates that high sulphidation ore is continuous with typical porphyry-skarn style chalcopyrite ore and that both have formed from mixing of magmatic with meteoric waters within a zone of fault offset.

Alteration and mineralization were localised within calcareous shale and thinly bedded limestone adjacent to the Grasberg Igneous Complex where they are zoned around fault offsets. Early phases of alteration are stratiform and are juxtaposed against the Idenberg Fault Zone, which has displaced host stratigraphy at least 600m vertically and possibly up to ~1,500m laterally. Four principal hydrothermal mineral associations are (1) calcic and magnesian skarn, (2) potassic assemblages including magnetite, (3) quartz-muscovite plus anhydrite and (4) locally massive pyrite. Cu and Au are associated with pyrite and occur discretely either as chalcopyrite ± bornite with an association of Cu-Au-Co (Zn-Pb) or as covellite ± enargite associated with Cu-Au (As-Sb-Hg). $^{40}\text{Ar}/^{39}\text{Ar}$ geochronology shows muscovite ($3.18 \pm 0.02\text{Ma}$) was coeval with potassic-biotite assemblages ($3.18 \pm 0.02\text{Ma}$ and $3.20 \pm 0.04\text{Ma}$). Calcic and magnesian skarn were derived from magmatic fluids ($\delta^{18}\text{O}_{\text{FLUID}} = 9-6\text{‰}$), while potassic and magnetite alteration were derived from high temperature ($>650^\circ\text{C}$), high salinity ($>50\text{wt}\%\text{NaCl}_{\text{EQUIV.}}$) magmatic fluids ($\delta^{18}\text{O}_{\text{FLUID}} = 6-12\text{‰}$). Quartz infill crystals associated with voluminous silicification contain a variety of fluid inclusions that range from moderate temperature ($T_{\text{H}} < 420^\circ\text{C}$) high and moderate salinity brines (35-55 and 15-30wt%NaCl_{EQUIV.}), to low density - low salinity vapour-rich fluid inclusions. Fluorite-hosted inclusions with lower T_{H} ($<300^\circ\text{C}$) and salinity ($\sim 5\text{wt}\%\text{NaCl}_{\text{EQUIV.}}$) are also related to quartz alteration. Quartz alteration, muscovite and anhydrite have estimated $\delta^{18}\text{O}_{\text{FLUID}}$ ranging from 0-6‰. δD data from magnesian skarn suggest that the magma source was strongly but variably degassed during skarn formation while clustering of biotite and tremolite δD data may indicate ponding of fluids prior to exsolution, which was preceded by monzonite dyke emplacement that were emplaced during skarn and potassic stage alteration.

Fluid infiltration was controlled by an active fault system characterised by strike-slip deformation overprinting a pre-existing reverse-slip fault. Periodic slip allowed infiltration of the magmatic fluids while a complex structural offset controlled the mixing of magmatic and meteoric fluids. Fluid mixing was augmented by phase separation which gave rise to brine and vapour-rich phases that migrated differently due to density contrasts. Ore deposition was related to mixing of magmatic and meteoric fluids, which resulted in an increase in H_2S relative to SO_2 , causing intense sulphidation of magnetite and precipitation of sulphides, beginning with gold-rich chalcopyrite-dominant mineralization. High sulphidation covellite-style mineralization occurred by contraction of the vapour phase that had separated from quartz-forming brines. Au, As and Sb were partitioned away from the high sulphidation copper mineralization due to higher solubilities of these metals as bisulphide complexes and deposited in distal pyrite along with chloride-complexed Pb and Zn.

Correction Notes (PhD) – Brian New

Page numbers as they appear here refer to the original review copies rather than the current edition of the thesis. This was followed as it was thought to be easier for review. Page numbers have changed through editing making the numbers presented below obsolete.

Chapter 1 – Introduction (pp1-22)

- Wilkins:
 - Sources added for figures 1-1, 1-3 and 1-4.
 - Figures 1-5, 1-7, 1-8, 1-9 and 1-10 made larger. Figures 1-8 and 1-9 clarity reduced due to printing hardware quality
- Friehauf:
 - Orientation comment added to figure 1-8
 - Names of faults added on page 12
 - Legend of figure 1-9 made larger for better legibility
 - Position of Lembah Tembagah described in figure 1-9 caption
 - Clear indication of what drill holes logged in this study for figures 1-12 and 1-13
- Richards:
 - Sources added/clarified for figures 1-1, 1-3, 1-4, 1-6, 1-7, 1-9
 - Details from caption of figure 1-9 added to text on page 13
 - Typos page 1, 3, 5, 7
 - References page 1 added to list

Chapter 2 – Host Rocks (pp23-46)

- Wilkins:
 - Annotations changed in Table 2-1
 - Stratigraphic names capitalized as suggested
 - Incorrect cross reference page 37
 - Included references to plates 2-9 and 2-10
 - Removed reference to hornfels on page 44
 - Included reference to plate 2-12 in text on page 44
- Friehauf
 - Grammar page 24
 - Standard abbreviations added to table 2-1
 - Clarification page 29
 - Hatch symbols explained for figure 2-2
 - Limestone-dolostone reference in plate 2-4a
- Richards
 - Typo table 2-1
 - Clarification figure 2-1

Chapter 3 – Paragenesis (pp47-81)

- Wilkins:
 - Grammar page 47
 - Missing labels is a computer translation error (*.doc to *.pdf), labels are present in final version
 - Pyrrhotite formula page 66
 - Terminology of hornfels-alteration and prograde-retrograde addressed in section 3-2
 - The paragenesis table required by Wilkins is embedded in Chapter 7 as it did not seem logical to place the conclusions before the evidence. The paragenetic sequence is an interpretation rather than a fact and the organization in the thesis reflects this.
- Frieauf
 - Grammar and clarification page 47
 - Grammar and clarification page 48
 - Wrapping figure 3-1
 - Grammar page 54
 - Grammar and clarification page 61
 - Grammar page 67
 - Clarification page 69
- Richards
 - Missing labels is a computer translation error and are present in final version
 - Grammar page 67
 - Grammar page 78
 - Clarification page 81

Chapter 4 – Structure (pp82-109)

- Wilkins:
 - Caption added for Figure 4-2
 - Caption for Figure 4-3, 4-4 and 4-5
 - Improved Legend for Figure 4-6
- Frieauf
 - Clarification figure 4-1
 - Clarification figure 4-6
 - Clarification figure 4-9
 - Clarification figure 4-10
 - Clarification figure 4-11
 - Grammar page 108
 - Grammar page 109
 - Clarification page 109
 - References

- Clarification page 110
-
- Richards
 - Clarification of authors work page 83
 - Spelling Figure 4-3
 - Spelling figure 4-8
 - Clarification page 109
 - Paragraph break page 111

Chapter 5 – Mineralisation (pp110-147)

- Wilkins
 - Figure 5-17, 5-22 placement corrected
 - Last sentence page 150 removed, speculative and unsupported
- Friehauf
 - Grammar page 112, paragraph 1 and 2
 - Expanded description page 113 para 3 (middle Waripi sandstone)
 - Caption spelling figure 5-3
 - Placement figure 5-17
 - Placement figure 5-22
 - Speculative statement removed page 146 “However, data in this....”
 - Spelling caption figure 5-23
 - Note on scientific clarity page 149 “chloride-complexed” not chlorine
 - Reference Crerar and Barnes, 1976
- Richards
 - Figure labels 5-1, cross references in text pp 113-114
 - Deformation control sentence page 114
 - Grammar paragraph 2 page 114
 - Legends figure 5-2, 5-3 and 5-4
 - Annotation figure 5-2 to 5-11
 - Improved Legend Figure 5-1
 - Cross reference page 129 (figure 5-12)
 - Comment of tilting of deposit post formation page 129
 - Grammar figure 5-13 caption
 - Grammar figure 5-14 caption
 - Caption order figure 5-18
 - Cross reference page 140 (figure 5-21)
 - Cross reference figure 5-20 caption (table 5-2)
 - Grammar 1st paragraph section 5.2
 - Grammar 3rd paragraph page 145
 - Cross reference page 146 (fig 5-13 and 5-14)
 - Missing word page 146
 - Note on microgeochemical study of sulphides and gold page 146
 - Section 5.2 has been reorganized by removing paragraphs concerning other deposits in district

- Grammar page 149
- Reference to Seward
- From the reading it is deduced that Richards' is actually suggesting a multivariate analysis be undertaken of element correlations. This is unnecessary as the element associations referred to are clearly evident in Figs. 5.5-5.11 and a more quantitative assessment is not required to support later discussion in the thesis

Chapter 6 – Fluid inclusions (pp148-174)

- Wilkins
 - Value changed 650 to 550, section 6.2.1
- Friehauf
 - Grammar tense, second sentence page 151
 - Clarification mineral species figure 6-3 and 6-4
 - Second image added to figure 6-6, inclusions represented by fluid inclusion type
- Richards
 - Section headings altered to properly define content
 - Issue of format translation (.doc to .pdf) for missing labels, labels are present in final version
 - Classification of inclusions, plate 6-4, 6-5 and 6-6
 - Clarity page 162 “some deeper”
 - Page 163, clarify SLV inclusions form high relief phases
 - Figure 6-2, note on bin ranges added to caption
 - Figure 6-3, note on bin ranges added to caption
 - Ice melting by inclusion type graph added to figure 6-4
 - Salt melting graph made to individual figure 6-5
 - Notes on high temperatures page 168.
 - Sentence removed p169 “All the high.....”
 - Grammar page 169 (comma inserted)
 - Alterations to opening statements section 6.2
 - Section 6.2.1 final statements removed
 - Paragraph on fluid inclusions on page 173 merged with paragenesis section, as to whether inclusions are primary, pseudosecondary or secondary
 - Rewrite of final section to consider models of fluid development from magma depth of emplacement, fluid separation and different magma sources
 - The fluid inclusions presented in the chapter have been reevaluated in terms of primary, secondary and pseudosecondary where possible and a note has been added that was not always possible to definitively assign a timing criteria to each. In addition, the definitive statements that a boiling assemblage is supported by the evidence is removed and reappraised to indicate that the observed inclusions plus homogenization temperature

data may support a boiling assemblage and that the weight of evidence points to a boiling assemblage.

- In his skepticism of the high temperatures assumed for quartz deposition Richards has ignored previous data in foundation papers (Wilkins, 1974) on fluid inclusion studies that indicated temperatures of formation $>700^{\circ}\text{C}$ as well as data collected locally at Grasberg from another researcher (Harrison, 2000).
- Standard phase change symbols have been used throughout the thesis and where they are impractical an explanation has been added to the figure caption. For examples, where all fluid inclusion data are presented in a graph relating to sample number it is not possible to identify which inclusions have homogenized vapour to liquid, liquid to vapour, or to salt. In these instances the symbol T_{FINAL} has been used.

Chapter 7 – Stable Isotopes (pp175-193)

- Wilkins
 - Figure 7-1 and 7-3, missing labels due to *.doc to *.pdf translation
 - Figure 7-2 increased in size to fill 2 pages
- Friehauf
 - Clarified who did analyses on opening page Chapter 7
 - Grammar section 7.1 page 176
 - Legend figure 7-1 problem with format translation
- Richards
 - Analytical people specified opening page chapter 7
 - Calcite instead of limestone opening page chapter 7
 - Grammar paragraph 1 section 7.1.1
 - Clarification of anhydrite values ($\delta^{18}\text{O}$) page 177 para 3 section 7.1.1
 - Temperature justification figure 7-2 added end of paragraph 2 section 7.1.2
 - Correction “due to preferential fractionation...” Section 7.2 opening paragraph. Sentence removed
 - Grammar paragraph 1 section 7.2
 - Incorrect reference (Campbell and Larson, 1998) paragraph 2 section 7.2
 - Note of high water-rock ratio added to sentence 3 paragraph 3 section 7.2
 - Possibility of mixing added paragraph 3 section 7.2
 - Figure 7-4 and 7-5 labelling
 - Note “at high temperature” added to sentence 3 on section titled “magmatic exsolution processes”
 - The suggestion by Richards for reorganization of the chapter along lines of isotope rather than data and analysis seems to be a matter of personal preference as the other two examiners were quite happy with approach taken
 - Assessment of possible errors in fractionation is present in the thesis as graphs of fractionation curves showing the position of the assumed

temperature. From these graphs it is possible to gauge the difference if a temperature of ± 50 , 100 or 150 degrees is assumed.

Chapter 8 – Geochronology (pp194-212)

- Wilkins
 - References for Mathur et al. (2000) and Mathur et al. (2005)
- Friehauf
 - Details of analytical personnel opening page Chapter 8
 - Note on word choice page 208 (indicates replaced by suggests)
- Richards
 - Repetition third sentence opening page removed
 - Analytical person clearly stated opening page chapter 8
 - Word choice page 194 (constituted replaced by consisted)
 - Figure labels page 197 file format translation (*.doc to *.pdf)
 - Grammar, section 8.1.2 (now 8.2) paragraph 1
 - Correction of age dates, section 8.1.2 (now 8.2) paragraph 2
 - Grammar, section 8.1.2 (now 8.2) paragraph 2
 - Discussion of age graphs copied from appendix to figure captions
 - Increased data on table 8-1 to include plateau and isochron ages
 -
 - Removed last sentence section 8.2 paragraph 2 to opening page chapter 8
 - Cross reference to figure 8-11 changed to table 8-3 in 1st paragraph “geochronology of the ertsberg mining district”
 - Grammar page 209

Chapter 9 – Discussion

- Wilkins
 - 1st note means as in text
 - Figure labels and cross references for figure 9-2, 9-3, 9-4 and 9-5
 - Figure 9-5 label
 - Cross reference figure 9-8 in 1st sentence-paragraph of section 9.3.2
- Richards
 - Grammar opening page Chapter 9
 - Grammar 1st paragraph section 9.1
 - Figure 9-1 caption reference and description of figure
 - Labels on Figure 4-5
 - Rearrangement paragraph 3 section 9.2.2 “the origin of...”
 - Reorder figure 9-6 and 9-7 to reflect sequence of cross references
 - Clarity paragraph 3 section 9.3.1 (economic interest and fO_2)
 - Reference and spelling Figure 9-6 (now figure 9-7)
 - Reference Figure 9-7 (now figure 9-6)

- 2nd paragraph section 9.1.2, “Fluid flow....*probably* produced”, “fluid infiltration *most likely* occurred”
- 1st paragraph 9.2.1, “Quartz alteration also.....*probably* not related....and *could be* interpreted...”
- 2nd paragraph 9.2.1 “Quartz alteration is closely....and this association *may* indicate...”
- 2nd paragraph 9.2.1 “Fluid dilution...*may also* have....”
- 2nd paragraph 9.2.1 “~~However,~~ *If phase separation of hydrothermal fluids did occur* at Kucing Liar...”
- 1st paragraph 9.2.2 “Higher degrees of local water.....” is now “A higher degree of local water interaction is believed to have promoted....”
- 1st paragraph 9.2.2 “The effect of reduced temperatures in the system was *probably*...”
- 3rd paragraph 9.2.2 ” Low salinity magmatic fluids related to covellite mineralization were *circulating* at temperatures...”
- 3rd paragraph 9.2.2 “Phase separation ~~appears to have been~~ *was probably* limited...”
- Discussion and Conclusions have been rewritten taking into account uncertainties and changed interpretations as required by Richards. In many instances this relates to the interpretation of the fluid inclusion assemblage where Richards believes that not enough information has been collected to support a boiling assemblage. Discussion with others at JCU and perusal of existing literature suggests that there is a weight of evidence that supports a boiling assemblage, however, the thesis has been revised to reflect the opinion of Richards.

1 Introduction

This thesis presents the results of a research program aimed at identifying the major controls of the porphyry-related Kucing Liar Cu-Au mineralised system. Porphyry-related mineralisation provided over 50% of the world's Cu production in the 20th century (Hedenquist and Richards, 1998) and these types of deposits are among the largest reservoirs of gold in the upper crust (Kesler, *et al.*, 2002). Economic Cu \pm Mo \pm Au deposits associated with porphyry magmas are concentrated at the margins of the Pacific Rim, occurring in North and South America, while in the southwest Pacific they are concentrated in Philippines, New Guinea and Indonesia (Figure 1-1). Due to the economic importance of porphyry mineralisation there is a large body of literature concerning this class of deposit. There is a wide variety of mineralisation styles associated with porphyritic intrusions including porphyry, skarn, epithermal and mantos that are enriched to varying degrees with Mo, Cu, Au, Ag, Pb and Zn (Figure 1-2).

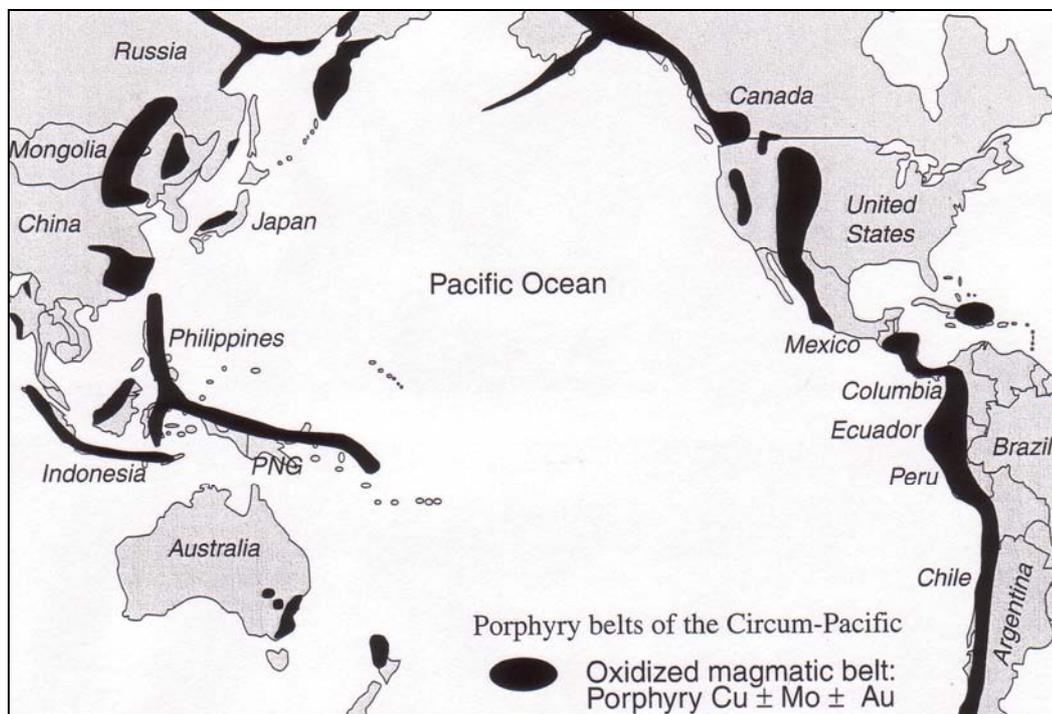


Figure 1-1 Distribution of porphyry Cu±Mo±Au deposits in the circum-Pacific region

Reproduced from Tosdal and Richards (2001)

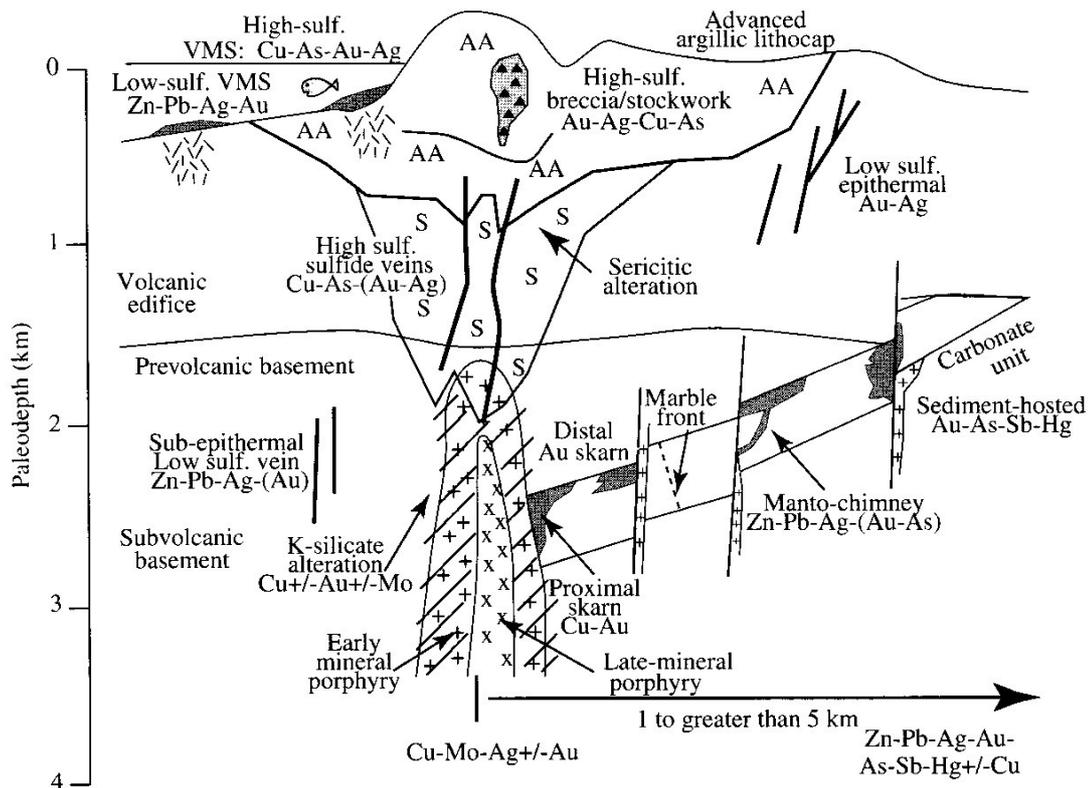


Figure 1-2 Ore deposit environments related to porphyritic intrusions

Schematic diagram showing the various forms of alteration associated with porphyry-related hydrothermal systems (figure 2 of Tosdal and Richards, 2001).

Kucing Liar is a Cu-Au mineralised system forming part of the Ertzberg Mining District, which is situated in the easternmost Indonesian province of Irian Jaya, now increasingly referred to as West Papua (Figure 1-3). PT Freeport Indonesia has been operating in the Ertzberg Mining District since 1967. Irian Jaya is part of the tectonic entity of New Guinea which includes a number of islands to the east which make up the Melanesian Volcanic Arc (Figure 1-4). New Guinea itself is dominated by a mountain range that extends the length of the island, commonly reaching elevations above 4,000m, referred to as the Papuan Fold Belt, which has a characteristic sigmoid shape from east to west and is noticeably wider in the middle of the island in the vicinity of the Papua New Guinea Highlands.

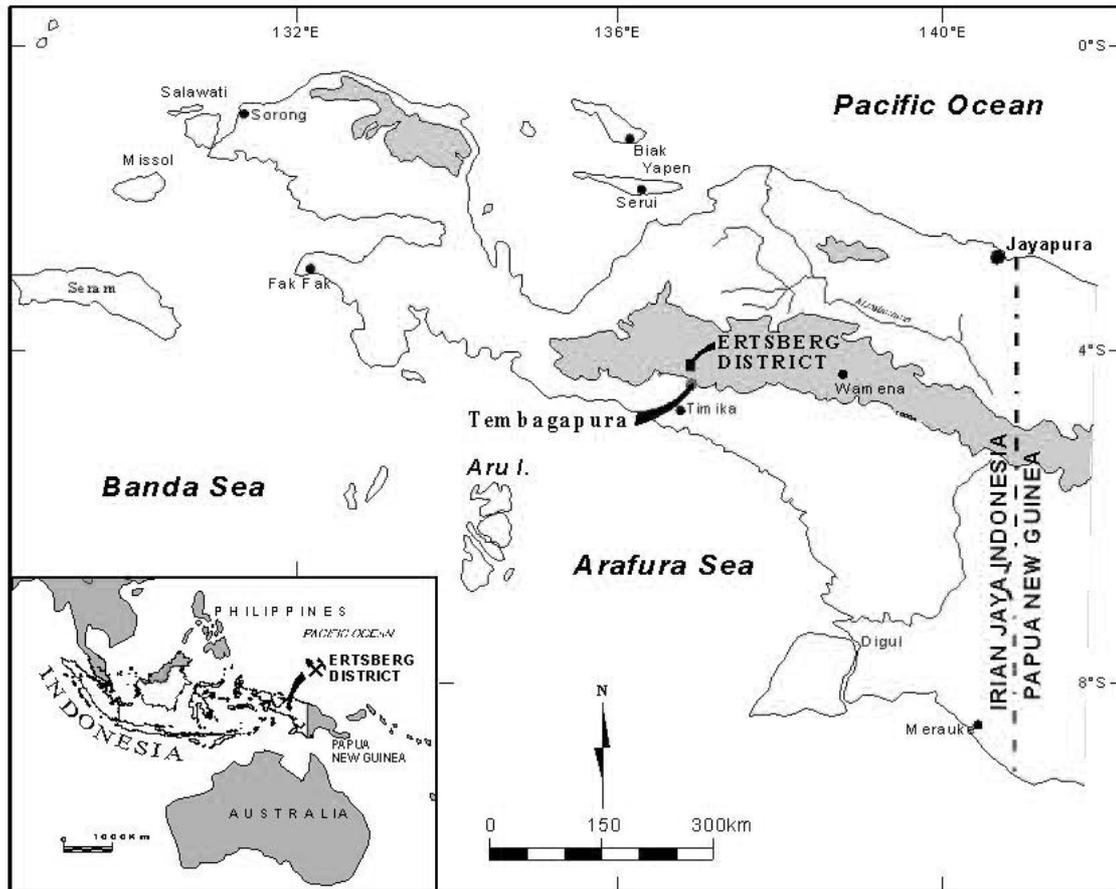


Figure 1-3 Location of the Ertzberg Mining District

Shaded area of map indicates areas above 1,000m elevation. Figure supplied by PT Freeport Indonesia.

The Ertzberg Mining District possesses the world's largest currently exploited gold resource and third largest copper resource, with the largest contribution being the Grasberg deposit. The Grasberg copper budget is of similar scale to the giant porphyry deposits of the southwest USA and Chile (Cooke *et al.*, 2005). The well-studied Bingham Canyon deposit in Utah has a similar copper inventory to Grasberg but significantly lower gold content. The deposits associated with the New Guinea tectonic system host the largest amount of copper and gold in the western Pacific (Garwin *et al.*, 2005). Papua New Guinea contains a large number of gold \pm copper deposits that are notably more gold-dominant than the Ertzberg mining district. At the time of data collection for this research (1998-2000), the Kucing Liar system was estimated to include 321Mt of ore containing 1.41% Cu and 1.41g/t Au. However, continued resource definition drilling has confirmed a larger resource of 478Mt of ore containing 1.29%Cu and 1.14g/tAu at Kucing Liar

(PT Freeport Indonesia, 2002 annual report). Within the district, nine major copper and/or gold occurrences have been delineated (Table 1-1), including gold-only resources (Wanagon) as well as copper-only resources (Lembah Tembaga) as well as other resources with variable grades and Cu:Au ratios. While Kucing Liar is much smaller than Grasberg, at ~540t of contained gold, it rates in the top 10 gold deposits of the world. The high copper *and* gold grades in such large quantities as well as the relationship to a richly gold-endowed island arc makes Grasberg and its related deposits unique amongst world-class porphyry copper deposits and so of particular interest in understanding their genesis. The different deposits found in the district display distinct and unique characteristics. Macdonald and Arnold (1994), Hefton *et al.*, (1995), and Pollard and Taylor (2002) have described the geology, alteration and mineralisation of the Grasberg Igneous Complex, while Mertig *et al.* (1994), Meinert *et al.* (1997) and Prendergast *et al.* (2005) have described the occurrences of sedimentary-hosted mineralisation in the district.

Table 1-1 Copper and/or gold resources of the Ertsberg Mining District

Deposit	Ore (t)	Cu (%)	Au (g/t)	Copper (t)	Gold (oz)
Grasberg	2,150,000,000	1.14	1.19	24,510,000	82,258,946
Kucing Liar	478,000,000	1.29	1.14	5,449,200	17,519,583
Ertsberg East Skarn System	185,000,000	1.58	0.71	2,923,000	4,223,065
Lembah Tembaga	90,000,000	1.50	na	1,350,000	Na
Big Gossan	37,349,000	2.69	1.02	1,004,688	1,224,833
Ertsberg	32,600,000	2.30	0.80	749,800	838,504
Dom	30,892,000	1.67	0.42	515,896	417,151
Wanagon	24,500,000	na	2.68	na	2,111,050
Wanagon (skarn)	2,400,000	1.94	0.95	46,560	73,305
TOTAL	3,030,741,000			36,549,144	108,666,437

Values from Harrison (2000). na=grade not available, assumed to be negligible. Note that Kucing Liar constitutes the second largest concentration of copper and gold in the district. There are currently no other economically viable resources in Irian Jaya outside the Ertsberg Mining District. Regional exploration followed by intensive delineation activities conducted by PT Freeport Indonesia has identified 8Moz of gold in the Wabu deposit associated with the Wabu Pluton, 35km to the northwest of the Ertsberg mining district (Sunyoto, 2000) that is currently considered subeconomic.

1.1 REGIONAL AND LOCAL SETTING

1.1.1 Geology of New Guinea and the Southern Central Ranges

New Guinea lies immediately to the north of Australia and includes a number of distinct topographic and tectonic zones. The main island is defined by a prominent mountain belt which extends the length of the island and possesses a number of peaks with elevations over 4,000m. The island of New Britain lies east of the New Guinea mainland while the Melanesian Volcanic Arc lies outboard of New Britain and includes New Ireland, Buka-Bougainville and Solomon Islands, and broadly parallels the Papuan Fold Belt (Figure 1-4). Deep sea trenches lying to the south of New Britain and to the west of Bougainville reach depths >8,000m. A shallower trench, 3,000-4,000m deep lies outboard of the Melanesian Volcanic Arc.

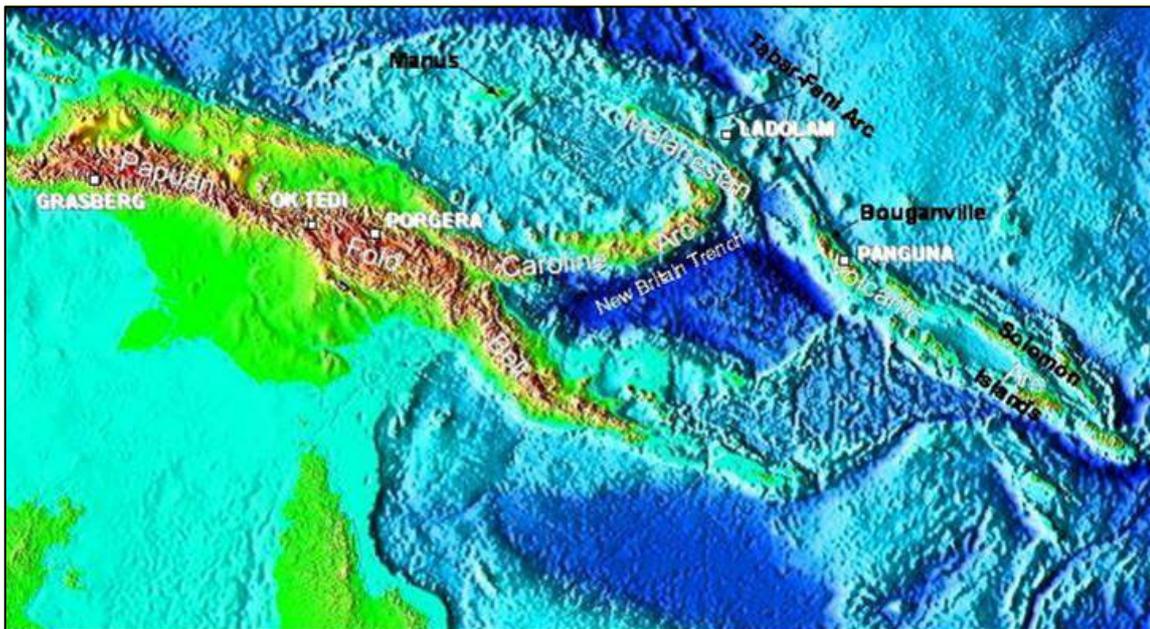


Figure 1-4 Physiography of Irian Jaya and Papua New Guinea

This digital elevation image shows New Guinea's extreme topography both above and below sea level. The Papuan Fold Belt is shown in orange and red colours of >1,000 and reaches >4000 in many locations, while the dark blue New Britain deep sea trench reaches depths of >8,000m. The locations of major porphyry-related deposits are indicated (image is a partial reproduction of picture acquired from website <http://www.ngdc.noaa.gov/mgg/image/2minsurface/1350/00N135E.jpg>, annotations added by author).

Tectonic evolution of New Guinea

The Papuan Fold Belt is the result of collision between the Australian continental plate and the Caroline and Pacific oceanic plates, which involved accretion of an island arc and ophiolite emplacement (Quarles van Ufford, 1996; Sapiie *et al.*, 1999; Warren, 2000; Hill *et al.*, 2002). The Jurassic age Irian Jaya ophiolite was emplaced along the northern margin of the Papuan Fold Belt (Figure 1-5). In Irian Jaya, the Derewo Metamorphic Belt separates accreted terranes from the sedimentary sequence of the Central Range. While the metamorphism of the Irian Ophiolite occurred during the Eocene (55-34Ma), metamorphism of the Derewo belt was initiated ~15Ma later in the late Oligocene (34-24Ma) to early Miocene (24-5Ma) (Weiland, 1999). Inclusion of metamorphic fragments in sediments of the Central Range indicates the Miocene development and denudation of a metamorphic fold belt (Weiland, 1999), which is indicated on Figure 1-5 by the development of a metamorphic core complex. South-directed subduction of the Caroline Plate ended in the Miocene (Solomon, 1990) and reversal to a north dipping subducting slab (Solomon Plate) beneath the easternmost remnants of the Caroline Island Arc (New Britain) occurred in the Pliocene (Figure 1-5). The Marumuni Arc developed in response to collision and accretion of the Caroline Island Arc along the northern margin of proto-New Guinea. The Pliocene magmatic arc on the New Guinea mainland developed in conjunction with the formation of the New Guinean Orogenic Belt (Papuan Fold Belt) (Figure 1-5). The current tectonic structure of the island changes in character and orientation from west to east. Irian Jaya is dominated by transcurrent faulting and stalled subduction, the middle part by transcurrent faults and slow convergence, and the eastern part by spreading ridges and active subduction (Figure 1-6a). Current tectonic activity is expressed by seismic activity and reveals a pattern of epicentres in which the deepest events are concentrated in belts that parallels plate contacts, particularly the New Britain subduction trenches, with decreasing depths westward. Only the shallowest earthquakes occur in Irian Jaya (Sapiie *et al.*, 1999). Porphyritic intrusions have been emplaced along the axis of the Papuan Fold Belt (Figure 1-6b). Two temporally distinct igneous suites on the mainland were intruded during Miocene (20-7Ma) and Plio-Pleistocene (<7Ma) times into the evolving collision environment

and form curvilinear arcs parallel to the elongation of the island and the tectonic plate boundaries (Figure 1-6b) (McDowell *et al.*, 1996). The older magmatic system is referred to as the Maramuni Arc while the younger is simply referred to as the Pliocene Arc. Both are areally restricted but more widespread in Papua New Guinea than in Irian Jaya (Figure 1-6b). Significant copper-gold mineralisation is restricted to the Pliocene Arc. Intrusions related to mineralisation in Papua New Guinea are both younger (e.g. Ok Tedi) and older (e.g. Porgera) than the age of intrusions in the Ertzberg Mining District (Figure 1-6b). Pliocene volcanoes are dotted about the mainland and adjacent island chains, including New Britain, Bougainville, and the Tabar-Feni chain outboard of New Ireland. On the mainland, volcanoes are noticeably clustered about the central Highlands as well as in lowland locations on the Papuan peninsula. Active volcanism continues to the present data in the islands off eastern New Guinea as evidenced by the explosion and extensive ash deposition from volcanoes near Rabaul in 1996.

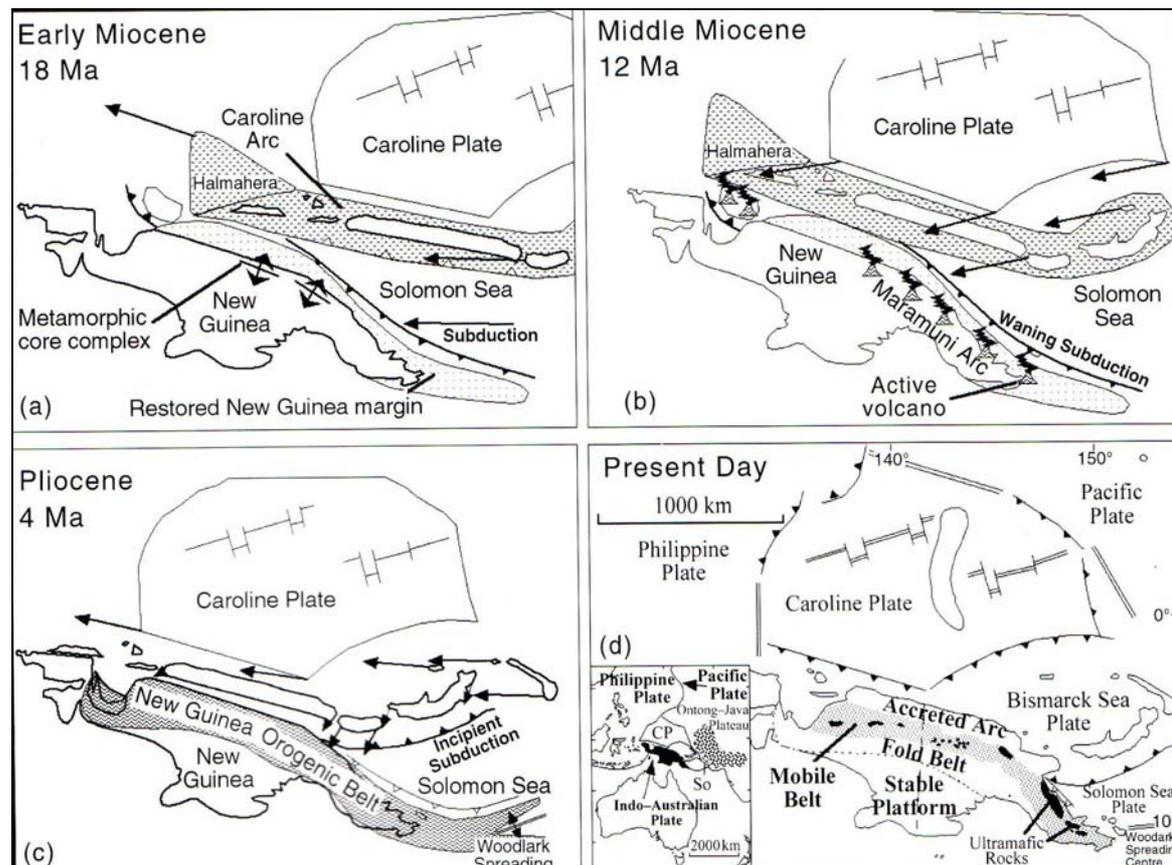


Figure 1-5 Palimpsestic reconstruction of the evolution of New Guinea

*A series of sketches illustrates the most significant events in the development of New Guinea and the age at which each event occurred. Reproduced from Figure 2 of Hill *et al.*, (2002).*

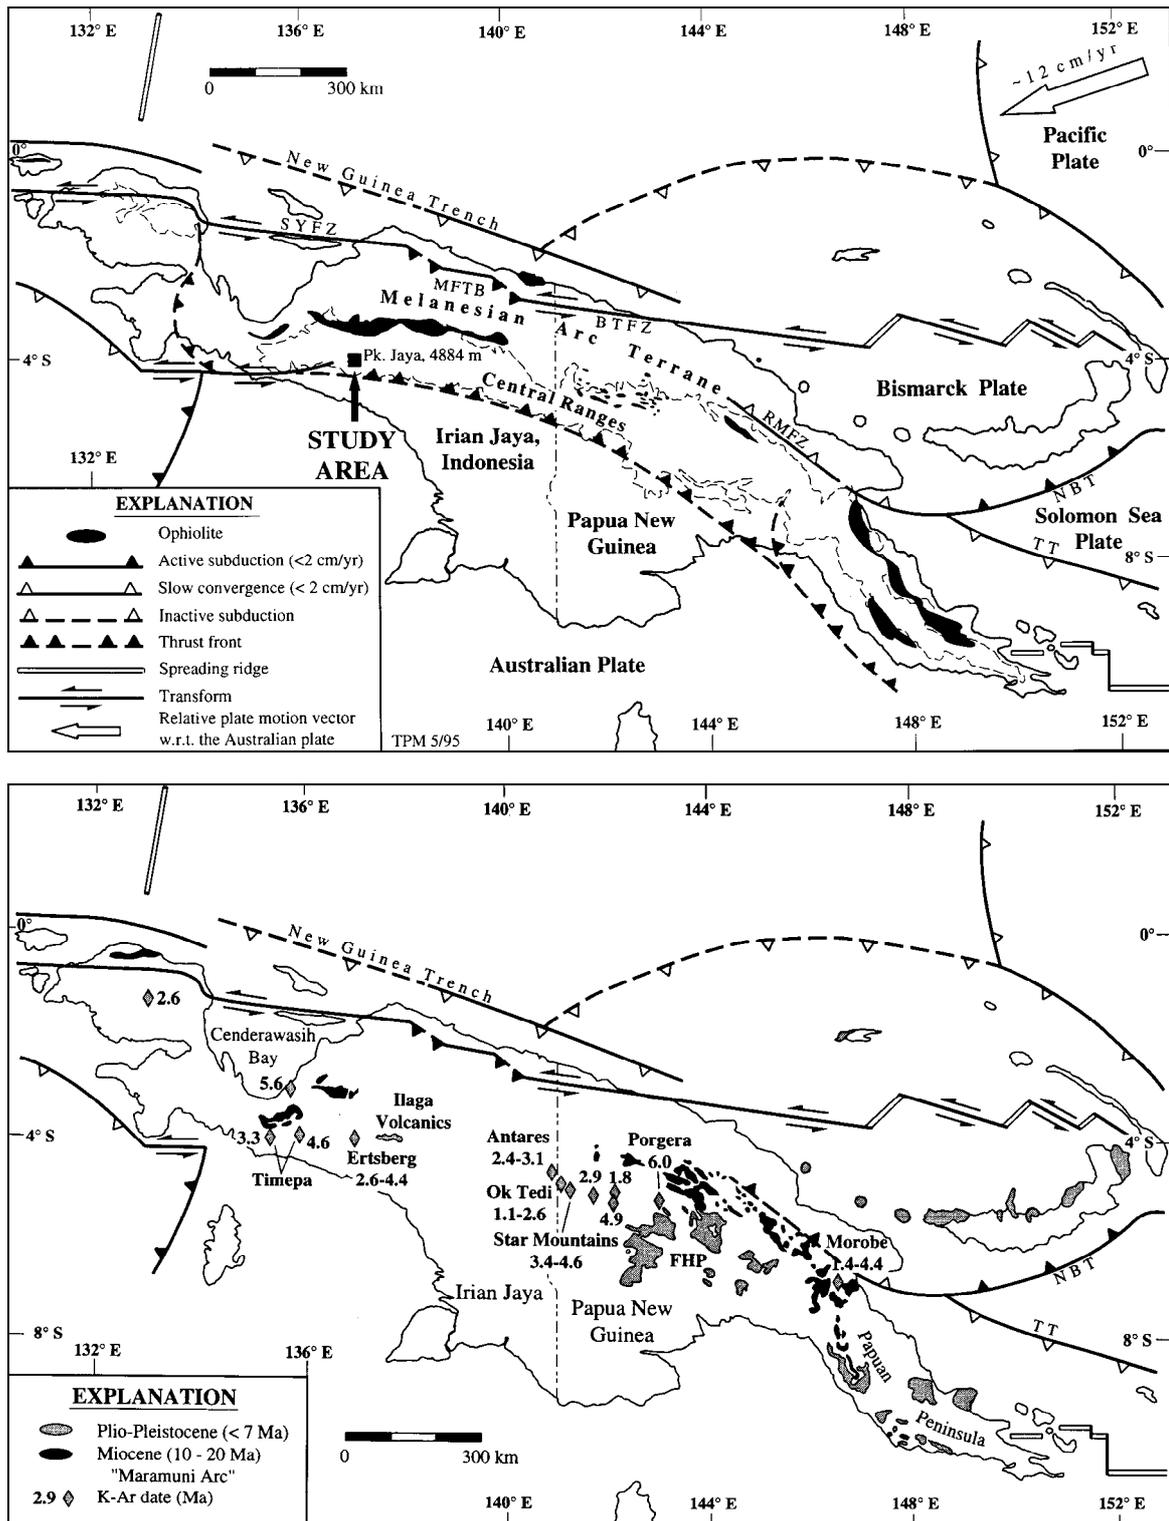


Figure 1-6 Tectonics and igneous intrusions of New Guinea (reproduced from McDowell *et al.*, 1996)

(a) Current convergence of the Pacific Plate is in west-southwest direction and subduction is restricted to eastern island arcs in the vicinity of New Britain and Bougainville. BTFZ = Bewani-Torricelli fault zone; MFTB = Mamberamo fold and thrust belt; NBT = New Britain trench; RMFZ = Ramu-Markham fault zone; SYFZ = Sorong-Yapen fault zone; TT = Trobriand Trough. (b) The Ertsberg mining district is indicated by the K-Ar age determination samples labelled "Ertsberg".

Stratigraphy and structure of the Southern Central Ranges

Collision tectonics in Irian Jaya have produced kilometre-scale folds and bedding-parallel sinistral strike-slip faults in the Ertsberg Mining District (Parris, 1994; Quarles van Ufford, 1996). In the vicinity of the Ertsberg Mining District, the sedimentary strata that comprise the mountain range are folded into a broad central syncline along the axis of the ranges. The stratigraphic sequence of the southern half of the Central Range now tilted and exposed along the road from Timika to Tembagapura (Pennington, 1995) reveals a sedimentary pile that was laid down discontinuously from Cambrian to Recent times (Figure 1-7). Thicknesses of stratigraphic units are consistent along strike (east-west) but vary across the axis (north-south) of the fold belt (Figure 1-7). Regionally, sedimentary strata are continuous along strike for hundreds of kilometres (Figure 1-8). The stratigraphic sequence here correlates with similar units in Papua New Guinea (Hill *et al.*, 2002). The strata in the Southern Ranges of Irian Jaya include thick sequences of mudstone, sandstone, limestone and dolostone ranging in age from Cambrian to Tertiary (Figure 1-7). Proterozoic pillow basalts at the base of the tectonic section are metamorphosed to lower greenschist facies and are strongly foliated in places. Mesozoic strata in the Ertsberg Mining District have equivalents in Papua New Guinea, but there are no Palaeozoic strata exposed in Papua New Guinea, where Mesozoic strata are underlain by granitoids and metamorphic rocks (Hill *et al.*, 2002).

In Irian Jaya, the mountain range associated with the Papuan Fold Belt is referred to as the Central Range, and the mountain-forming event is named the Central Range Orogeny (Quarles van Ufford, 1996). The Central Range fold and thrust belt is marked at its southern margin by a thrust fault named the Mapenduma Thrust and to the north by the Derewo Metamorphic Belt (Figure 1-8). The southern Central Ranges is an area of tilted and folded Australian continental margin sediments lying between two thrust faults which separate the Papuan Fold Belt from the Derewo Metamorphic Belt to the north and flat-lying margin sediments to the south. A sharp change in topography marks the location of the Mapenduma thrust. The Central Range between the Mapenduma Thrust and the Derewo Metamorphic Belt is dissected by oblique faults, which

visibly offset stratigraphy with a left-lateral sense of displacement (Figure 1-8). These arc-oblique faults are traceable for long distances on the map and connect between the Derewo and Mapenduma Faults (Figure 1-8). They are accompanied by faults with much shorter lengths that are subperpendicular to the fold belt and have a left-lateral sense of displacement. A third set of faults strikes east-northeast but is not as well defined by stratigraphic offsets as the arc-oblique and arc-normal faults. The Ertsberg Mining District is associated with arc-oblique faults though less clearly associated with arc-normal faults (Figure 1-8). Igneous intrusions and volcanic fields are also related to east-northeast striking faults as demonstrated by the Ilaga Volcanic Field lying to the east of the Ertsberg Mining District (Figure 1-8). Mineralised intrusive bodies are also associated with thrust faults as demonstrated by the relationship of the Wabu Pluton with the Derewo Fault (Sunyoto, 2000), within the Derewo Fault (Figure 1-8).

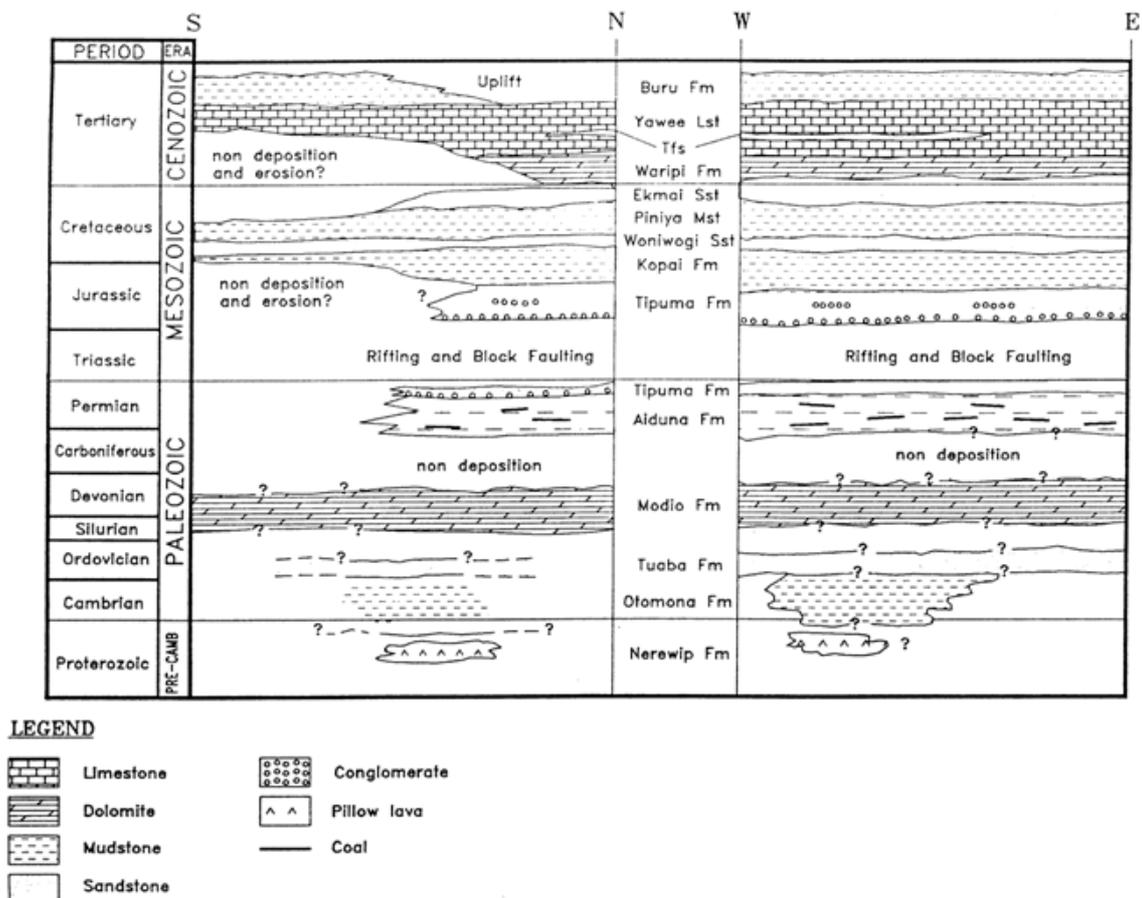


Figure 1-7 Sedimentary record of the Timika-Tembagapura region (reproduced from Parris, 1994a).

The section indicates lateral continuity from east to west along the continental margin but variable thicknesses from north to south, perpendicular to the margin.

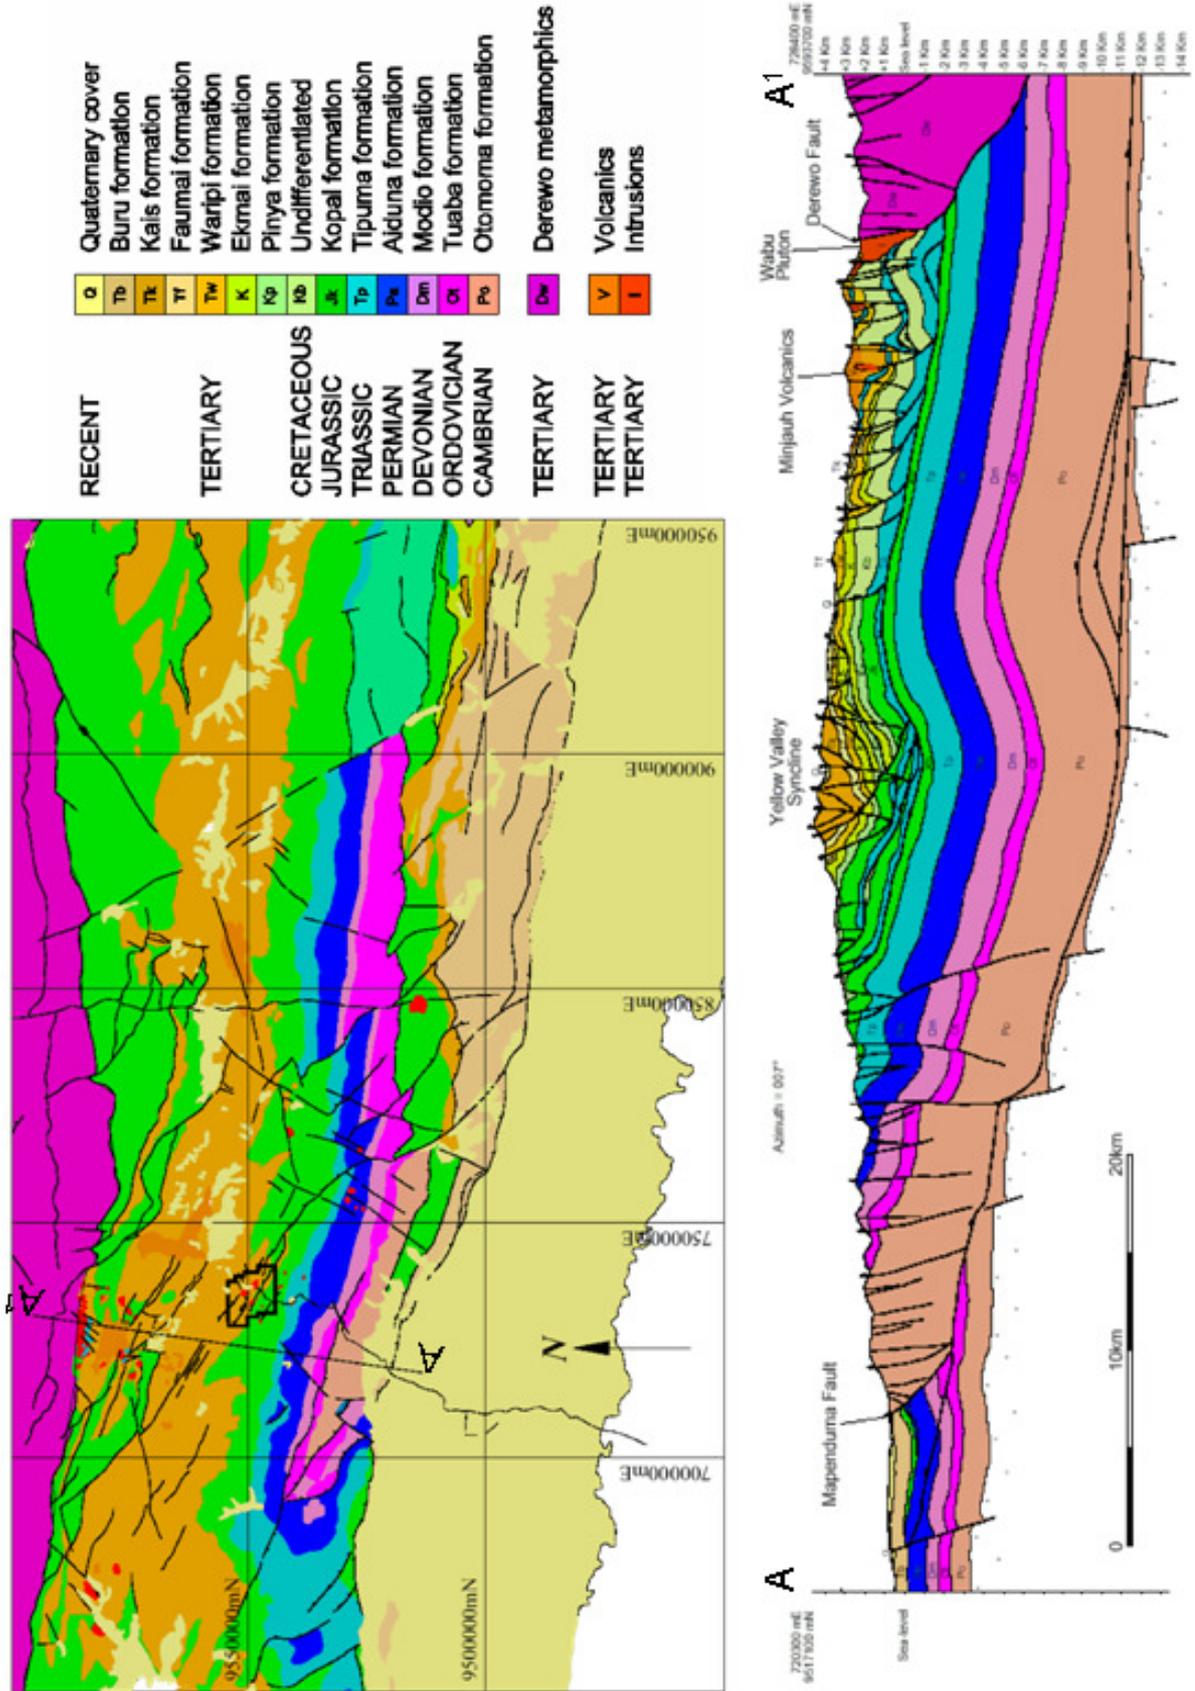


Figure 1-8 Geology of southern flanks of the Central Range
 Black box = CoWA (Contract of Work, block A). Map modified from Parris (1994b).

1.1.2 Geology of the Ertzberg Mining District

The geology of the Ertzberg Mining District has become well understood due to local, district and regional research programs on tectonostratigraphy (Quarles van Ufford, 1996; Weiland, 1996), structural controls (Sapiie, 2001), intrusive bodies (McMahon, 1996), and individual deposits (Macdonald and Arnold, 1994; Mertig et al., 1998; Meinert et al., 1998; Widodo *et al.*, 1998; Pollard and Taylor, 2002; Prendergast, 2004). Units in the mine district have experienced ~5km of uplift associated with 100km-scale-shortening manifest in large-amplitude folds and high angle reverse faults (Quarles van Ufford, 1996). The district includes the axial zone and southern limb of the regional-scale Yellow Valley Syncline (YVS) that is cross cut by arc-parallel, -oblique and -normal faults. The Yellow Valley Syncline trends parallel to the Central Range and plunges shallowly northwest (Figure 1-9). The northern and southern limbs have been disrupted by steeply dipping bedding parallel faults that have displaced the core of the syncline upwards relative to the limbs.

Tectonostratigraphic data for Irian Jaya (Quarles van Ufford, 1996; Sapiie *et al.*, 1999) record a history of folding and reverse faulting from 12-4Ma followed by left lateral fault movement between 4-2Ma. Symmetric and asymmetric repetition of stratigraphic marker horizons such as the Sirga sandstone and the Tk2 layer within the Kais Limestone (Figure 1-9) indicate that both folding and thrusting has occurred. Major thrust displacement is apparent along the Wanagon Fault. In addition to thrust faulting, left lateral movement is documented for the large faults in the Ertzberg Mining District that trend subparallel to stratigraphy (Sapiie, 2000; Sapiie and Cloos, 2004). These strike-slip faults (Wanagon, Idenberg Nos 1 & 2, Ertzberg Nos 1, 2 & 3) have reported displacements of 1,500m (Figure 1-9). Other faults are visible and strike northeast to east-northeast. This set of faults has smaller apparent left-lateral displacements and includes the New Zealand Pass Fault and the Grasberg Fault, which intersects the Yellow Valley Syncline in the vicinity of the Grasberg Igneous Complex (Figure 1-9).

Igneous units in the Ertsberg Mining District have been intruded as columnar and elongate bodies into the axis and limbs of the Yellow Valley Syncline in the form of the Grasberg Igneous Complex and the Ertsberg Intrusive Suite (previously described as undifferentiated Ertsberg porphyry). The Grasberg, Kay and Lembah Tembaga intrusive complexes have near circular outcrop pattern (though the latter occurs beneath Lake Wanagon), while the Ertsberg and Wanagon intrusions are elongate parallel to the main strike (see Figure 1-9). The Grasberg Igneous Complex (GIC) occupies the axis of the Yellow Valley Syncline where it is intersected by the high angle Grasberg Fault. The Ertsberg Intrusion is controlled by the Ertsberg No1, No2 & No3 faults to the east and the Idenberg No1 & No2 faults to the west (Figure 1-9). Similarly, the Wanagon Sill appears to be related to the position of the Wanagon Fault. The Kali dykes are the youngest intrusive phases and appear to have intruded into the centre of the Grasberg Igneous Complex parallel to the axis of the Yellow Valley Syncline. These intrusions were emplaced at ≤ 2 km, and sourced from depleted mantle with small contributions from an ancient, enriched mantle reservoir (McMahon, 1994b; Housh and McMahon, 2000). They are divided into a high-K group (latites, trachydacites and trachytes) and a low-K group (medium to high-K andesite and dacite); the high-K group includes the Grasberg Igneous Complex and Ertsberg Intrusive Suite (McMahon, 1994a; McMahon, 1994b).

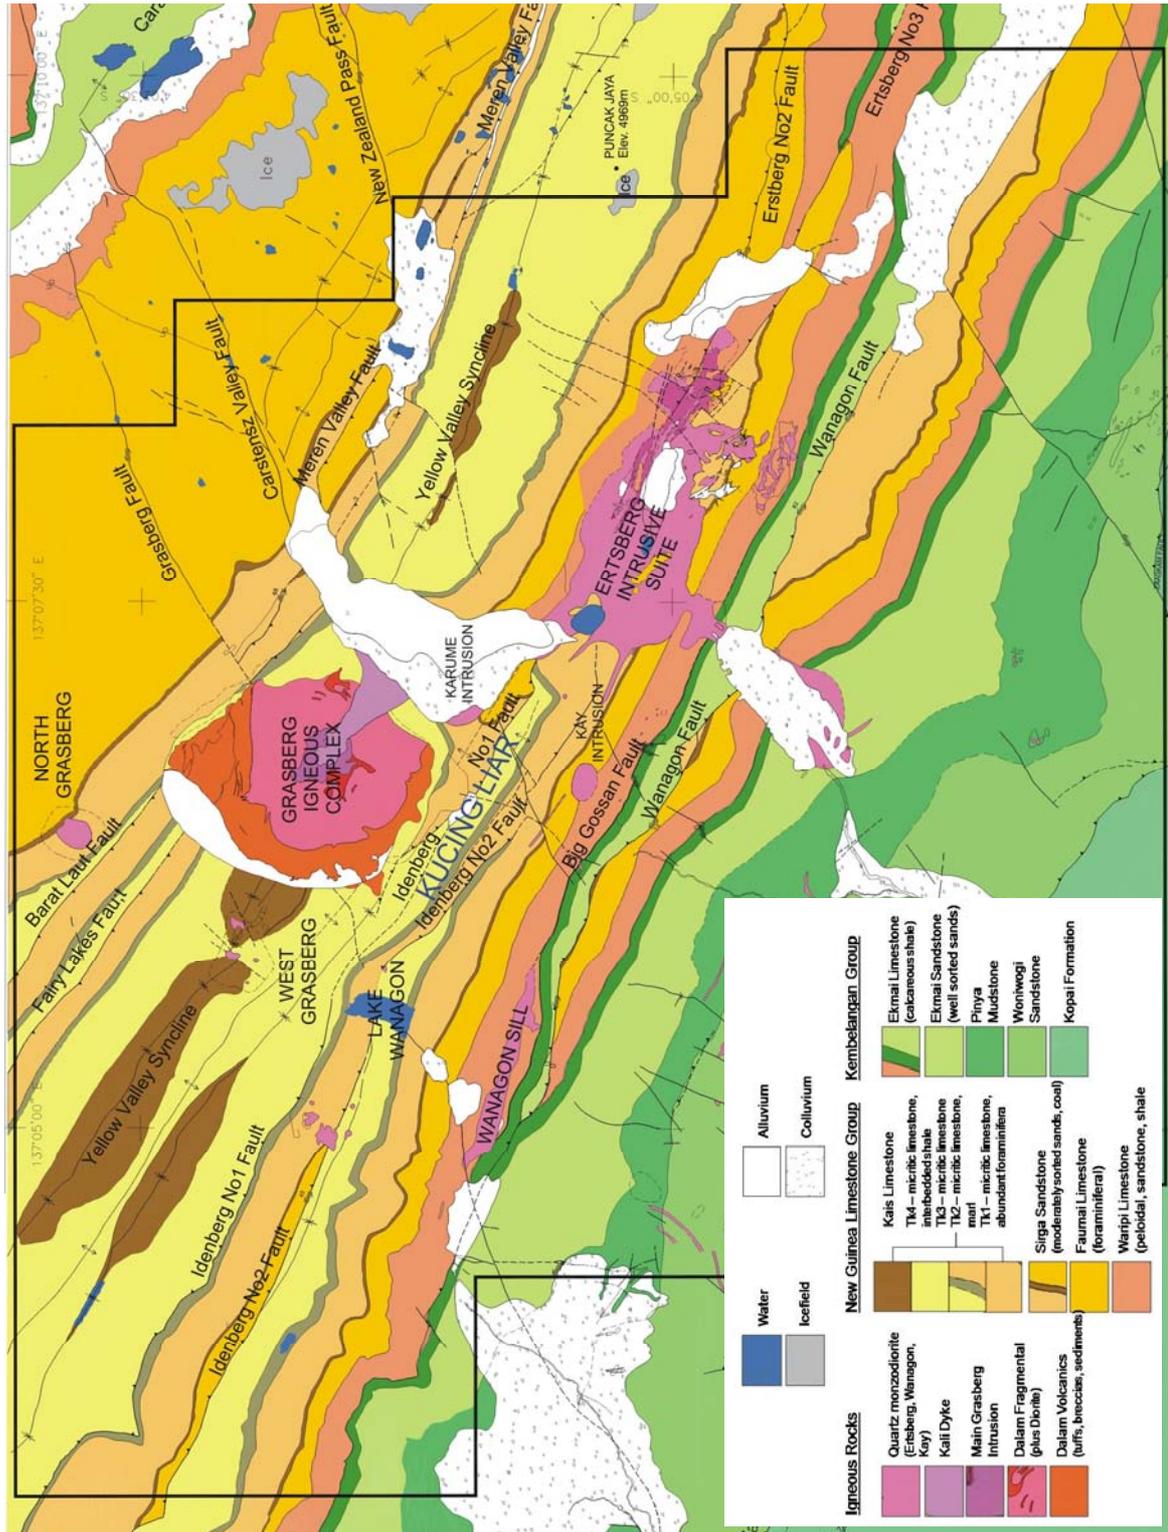


Figure 1-9 Geological map of the Ertsberg Mining District (supplied by PT Freeport Indonesia) *Cretaceous* units are shown in green colours and *Tertiary* units in brown; intrusions are red to pink coloured. Kucing Liar is adjacent to the Grasberg Igneous Complex, and along strike from the Ertsberg Intrusive Suite to the east and the Lembah Tembaga (beneath Lake Wanagon) porphyry intrusion to the west.

1.2 ACCESS AND METHODS

1.2.1 Physiography of the mining district

Kucing Liar is situated within the Ertsberg Mining District near the watershed of the Central Ranges of West Papua. The Ertsberg Mining District was originally centred on the Ertsberg deposit, and occupies roughly 100km² of the deeply incised south flank of the Central Ranges of Irian Jaya. The mine site lies at, and above the vegetation line. Ice accumulations fringe mountain peaks just 5km from the mine site, that in the past were true glaciers flowing directly past the present mine site, just 4°S of the equator (Quarles van Ufford and Sedgwick, 1998). The district boundary, originally square, was altered to exclude icefields which are now part of the adjacent Lorentz nature reserve, which covers a large area from the middle of the Central Range to the low-lying areas adjacent to the ocean. Topography in the mine district is severe (Plate 1-1) with elevation ranging from 2,000m to 4,880m. The northern boundary of the district is in the highest elevations of the Central Ranges mountain belt which reaches its maximum of ~4,884m at the nearby peak of Puncak Jaya. Mining in the district was originally concentrated on the Ertsberg deposit before moving to the Ertsberg East Skarn System (EESS), which continues to supplement the current primary mining activity at Grasberg. Both Ertsberg and Grasberg are open pit mines while the EESS is mined via large-scale underground block caving methods. Grasberg mineralisation is centred on the Grasberg Igneous Complex while four deposits are situated at the periphery of the Ertsberg Intrusion hosted by sedimentary rocks, namely the Ertsberg, Ertsberg East, Dom and Big Gossan skarn systems.

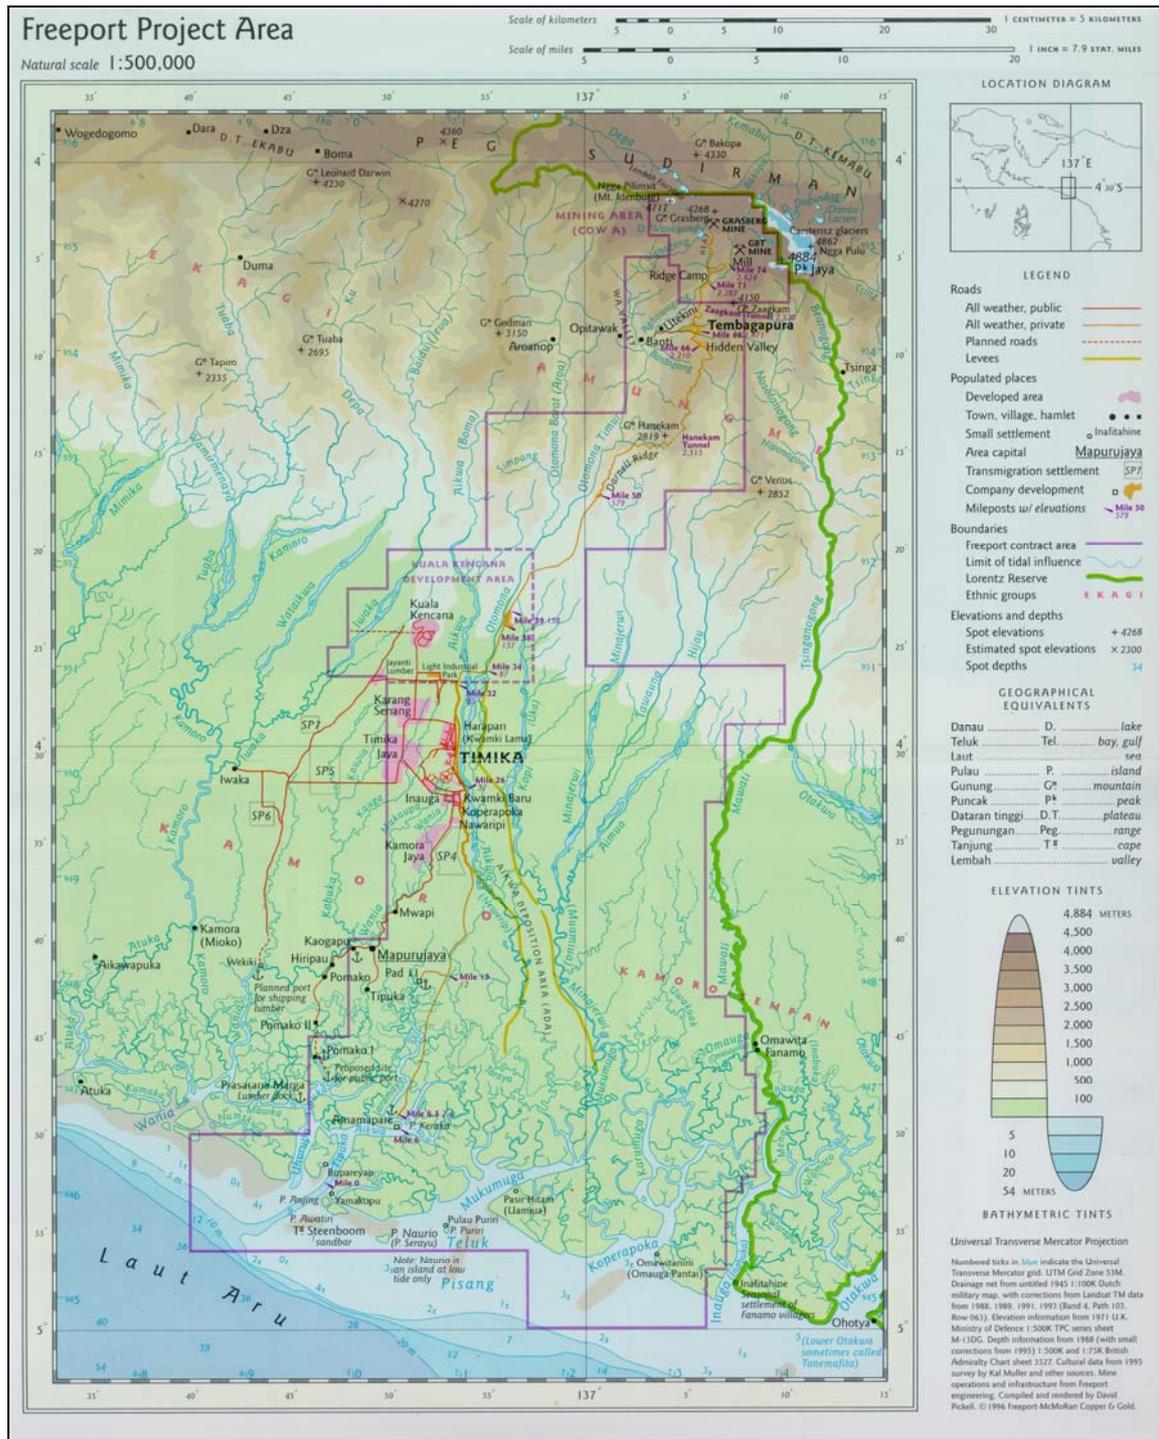


Figure 1-10 Physiography of the Southern Ranges and Ertsberg Mining District

A plan of the regional geography and operational infrastructure of the Ertsberg mining district. A road constructed by Freeport connects the port of Amamapare, the airport town at Timika, the mine town of Tembagapura and the mill site over a distance of 124km, reaching an elevation of 2,800m. Ice fields, formerly glaciers are visible at upper right of the figure coloured white and blue. There are mile distances and spot elevations in metres included along the road connecting the port to the mine site. Reproduced from Mealey (1996).

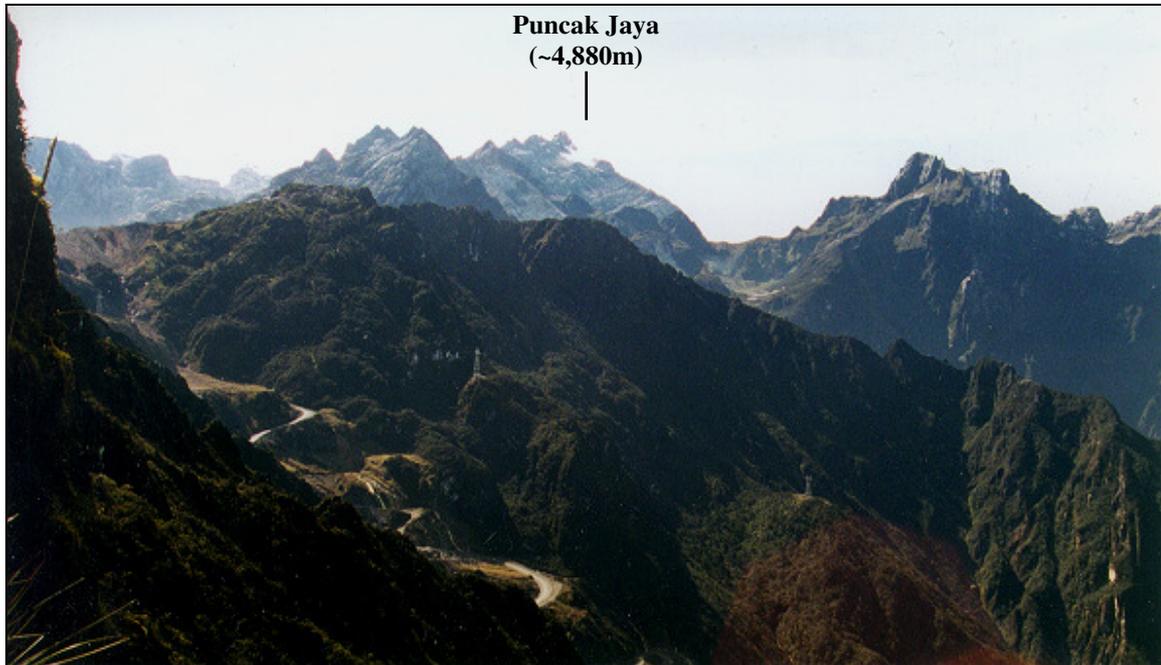
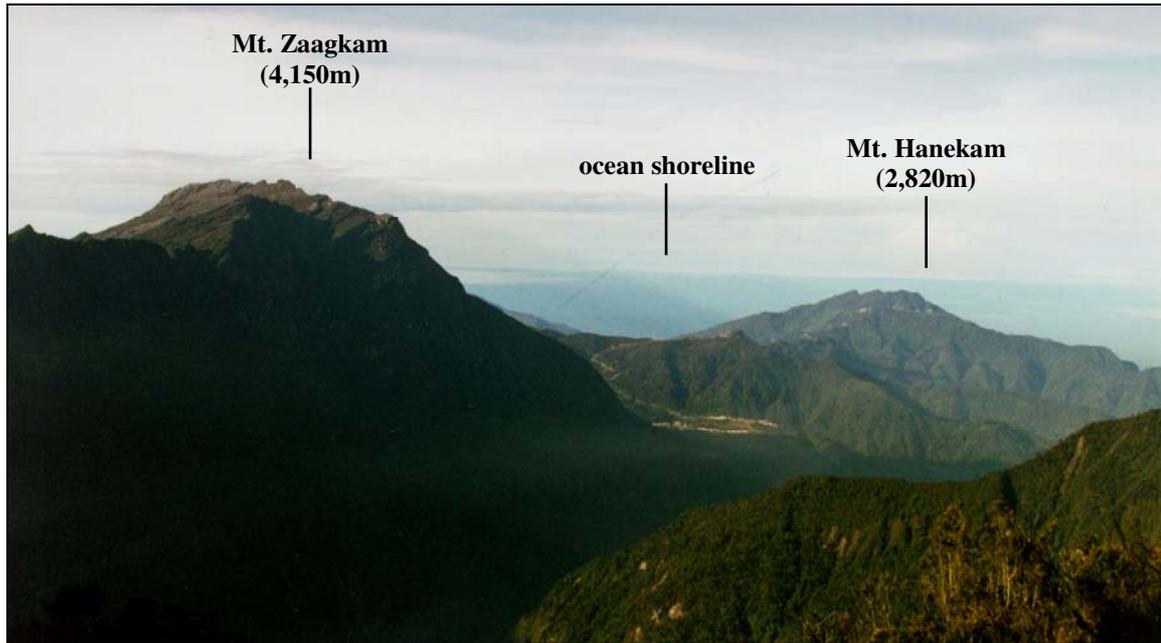


Plate 1-1 Relief of the Ertzberg Mining District and access routes

(a) View looking south from the Ertzberg Mining District between the 4,150m Mt Zaagkam and the 2,820m Mt Hanekam. The collection of buildings visible at lower centre is Hidden Valley, perched at the top of the steep-sided valley where Tembagapura is located. The access road connecting Timika, Tembagapura and the mill site is visible tracking along ridge tops between Mt Zaagkam and Mt Hanekam. (b) A view looking east toward Puncak Jaya, the highest mountain in Southeast Asia. The Grasberg open pit mine operations are to the left of view. The Heavy Equipment Access Trail (HEAT), which provides access to the mine, is visible in foreground. The Kucing Liar deposit occurs at depth below the north-south trending ridge in the middle of picture, with the Big Gossan skarn deposit located further to the south (right). Power pylons are perched on smaller ridges in the foreground of this ridge.

1.2.2 Sources of data

A detailed history of exploration and mining in the Ertzberg Mining District, including initial exploration for Kucing Liar is included in the book *Grasberg* (Mealey, 1996). Kucing Liar, meaning “wild cat” in the Indonesian language, was actively explored for in favourable sedimentary units adjacent to the Grasberg Igneous Complex following discovery of mineralised country rock fragments at the margin of the Grasberg Igneous Complex in 1992 and high-grade intersections during deep exploration in 1994 (Macdonald, *pers. comm.*). The Grasberg Igneous Complex is a wineglass shaped body composed of multiple igneous bodies in its stem and of heavily fragmented zones overlain by layered pyroclastic rocks in the flared upper zone. A tunnel driven at 3000mRL into the Grasberg Igneous Complex from the mill to control water influx into the Grasberg open pit intersected significant mineralisation associated with a fault and was given the name Amole, meaning, “welcome” in the local Amungme language. A second level driven northwest subparallel to the dominant strike of stratigraphy provided a platform for delineation of this zone by diamond drilling (Figure 1-11). Drill stations spaced evenly along strike confirmed that the Amole mineralised zone was contiguous with Kucing Liar (“wild cat”) intersections some 800m further west on the access trail to Grasberg. Excavations spaced at 50m intervals along this drive were completed for drilling stations, of which 16 were originally completed spaced 100m apart covering 1,500 metres of regional stratigraphic strike (Figure 1-12). Later infill drilling was conducted in the centre of deposit to confirm continuity of the resource at a distance of 50m, the core from these holes have been inspected but not included in the dataset for the current research project. Drilling was conducted in radial patterns on azimuths of 39 or 219° (Figure 1-12), perpendicular to the regional strike (Figure 1-13). Collar positions and downhole survey orientations for all drilling are recorded in Appendix 1.

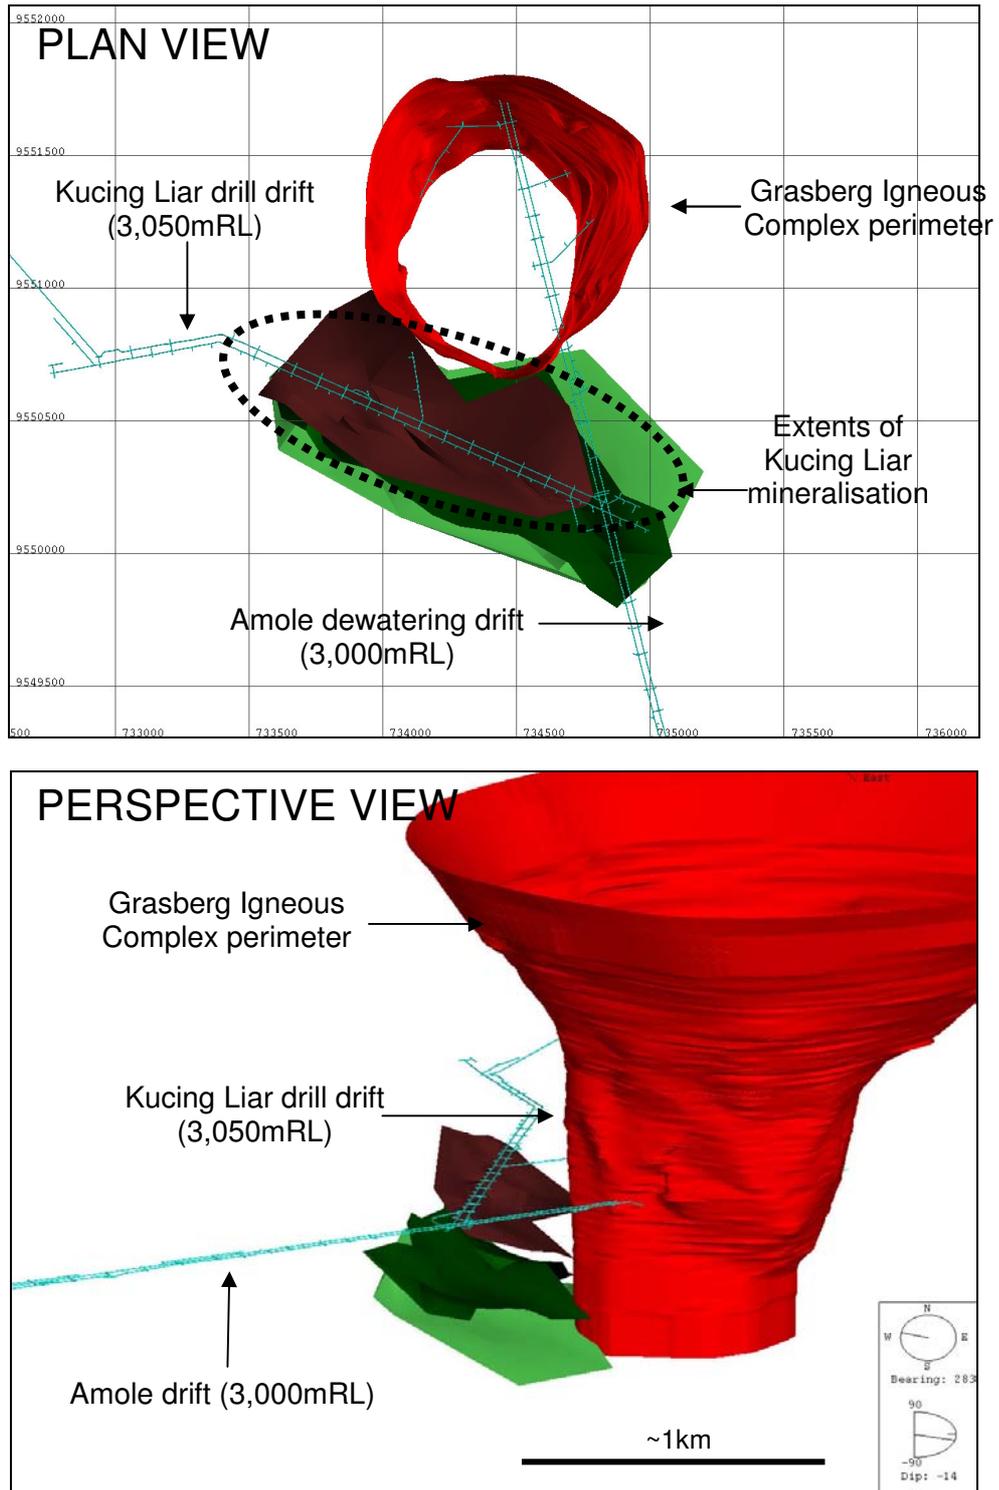


Figure 1-11 Position of Kucing Liar mineralisation relative to Grasberg Igneous Complex
Plan and perspective views illustrate the location of Kucing Liar with reference to Grasberg as well as dewatering and delineation tunnels. The outer perimeter of the Grasberg Igneous Complex (supplied by Peter Manning of PT Freeport Indonesia) is coloured red while the Kucing Liar mineralised zone is represented by three surfaces representing major internal stratigraphic contacts that are coloured brown, dark green and light green. Underground access levels are shown in light blue. The perspective view has no vertical exaggeration.

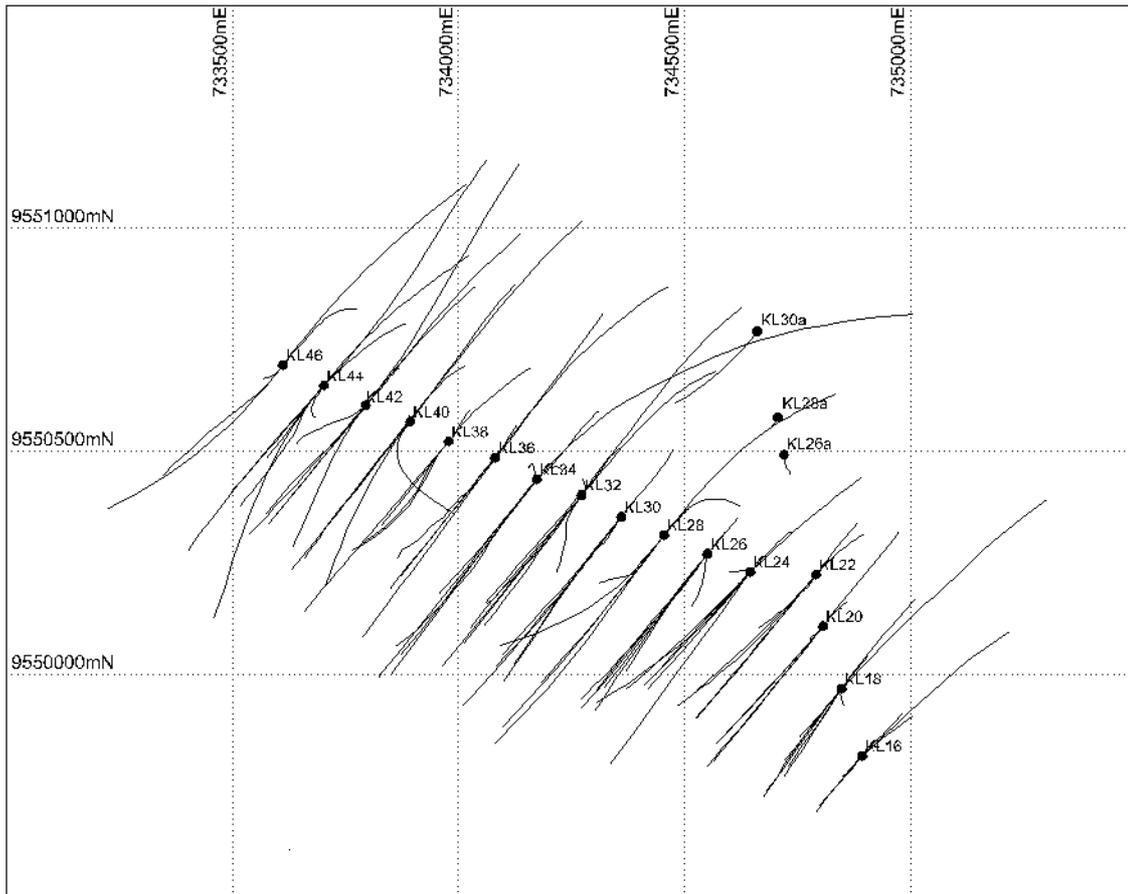


Figure 1-12 Plan view of all Kucing Liar drill traces logged for this research program

Plan view of drilling including all holes sampled and measured for this research program. The traces of drilling are projected in plan view and many overlie each other. The filled circles represent the location of the collars and the drill station position. Compare with Figure 1-11. The drill stations are labelled with the prefix KL, followed by the station number and a number exclusive to each hole (eg. KL16-03, KL32-04). KL26-11, KL28-9 and KL30-9 were collared from the Amole dewatering drift. The dip and azimuth of each drill hole have been surveyed every 3m on average and this data has been used to position each interval.

Holes were nominally divided into 3m lengths by PT Freeport Indonesia geologists for assaying but shortened if a change in geology was identified. A short length of drill core (10-20cm) was removed from each assayed interval and retained, producing an archive of “skeleton” core. All of the drill holes in Figure 1-12 and Figure 1-13 were logged using these samples on two separate occasions from Sept.-Nov. 1997 and June-Sept. 1999. The second period of logging revisited many of the drill holes logged on the first occasion. Due to the location and the extreme elevation (Plate 1-1), no field mapping was conducted for this research project, though one visit was made to a baseline stratigraphic section that was considered equivalent to the Kucing Liar host rocks.

Figure 1-13 Layout of all holes in each drill station logged for this research program


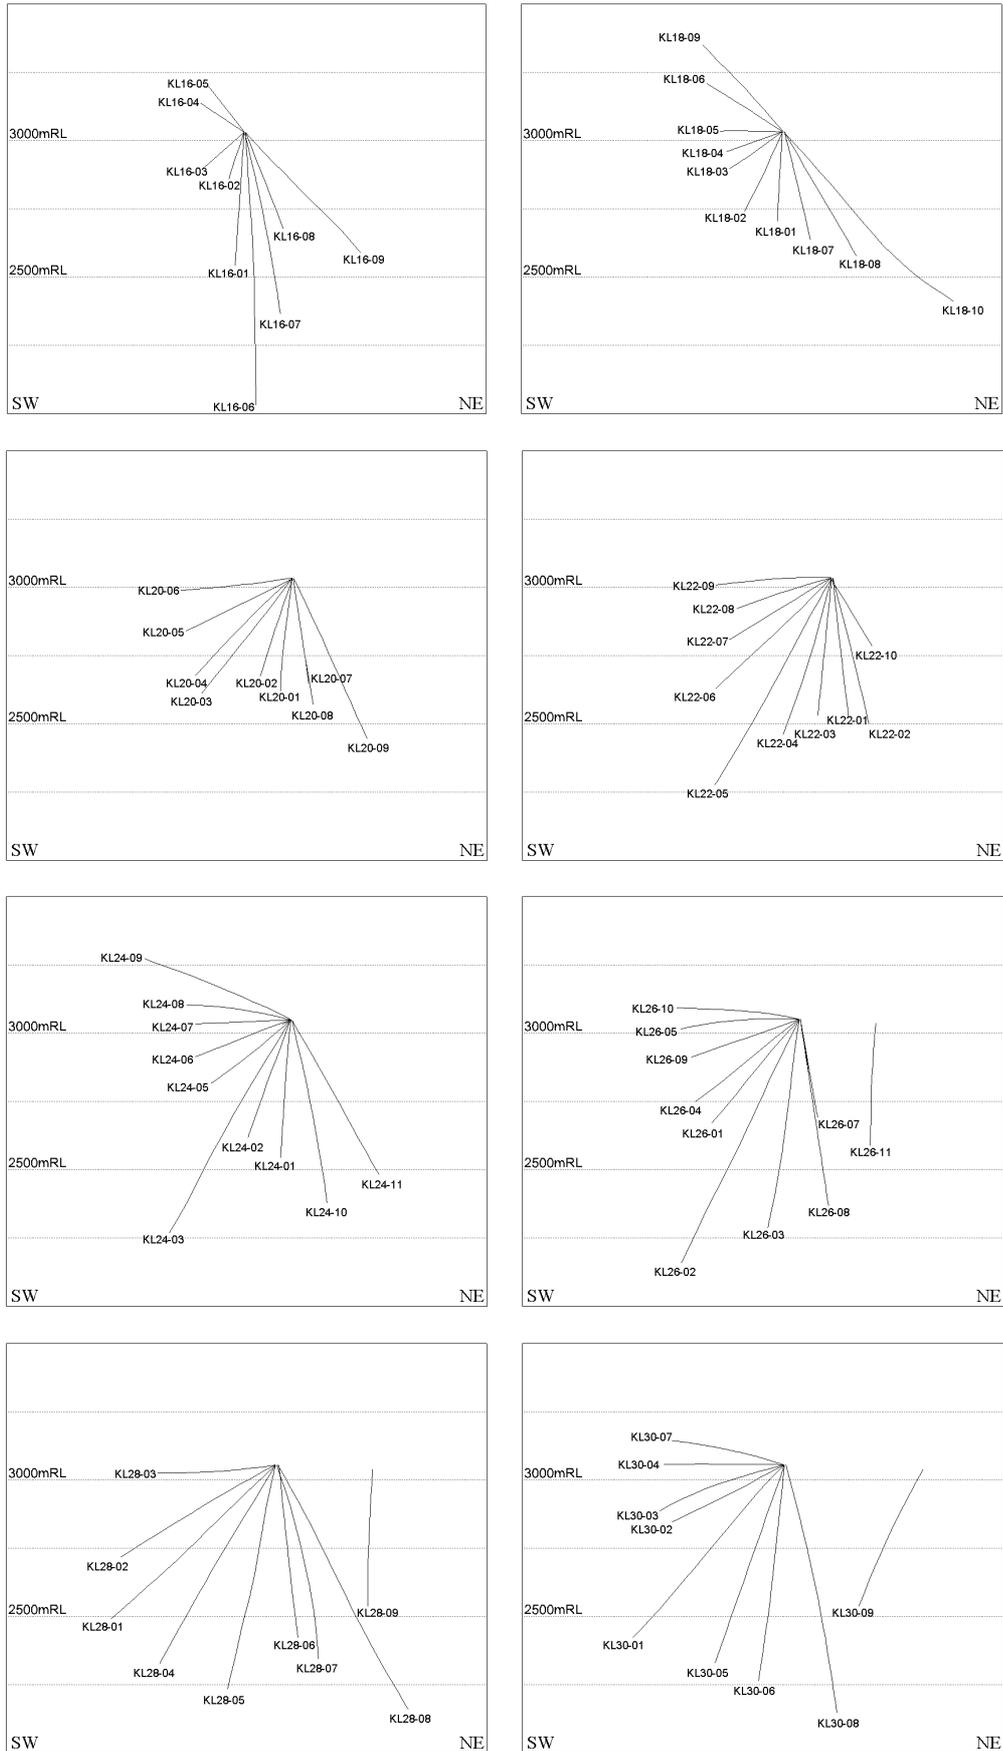


Figure 1-13 Layout of all holes in each drill station logged for this research program (cont.)

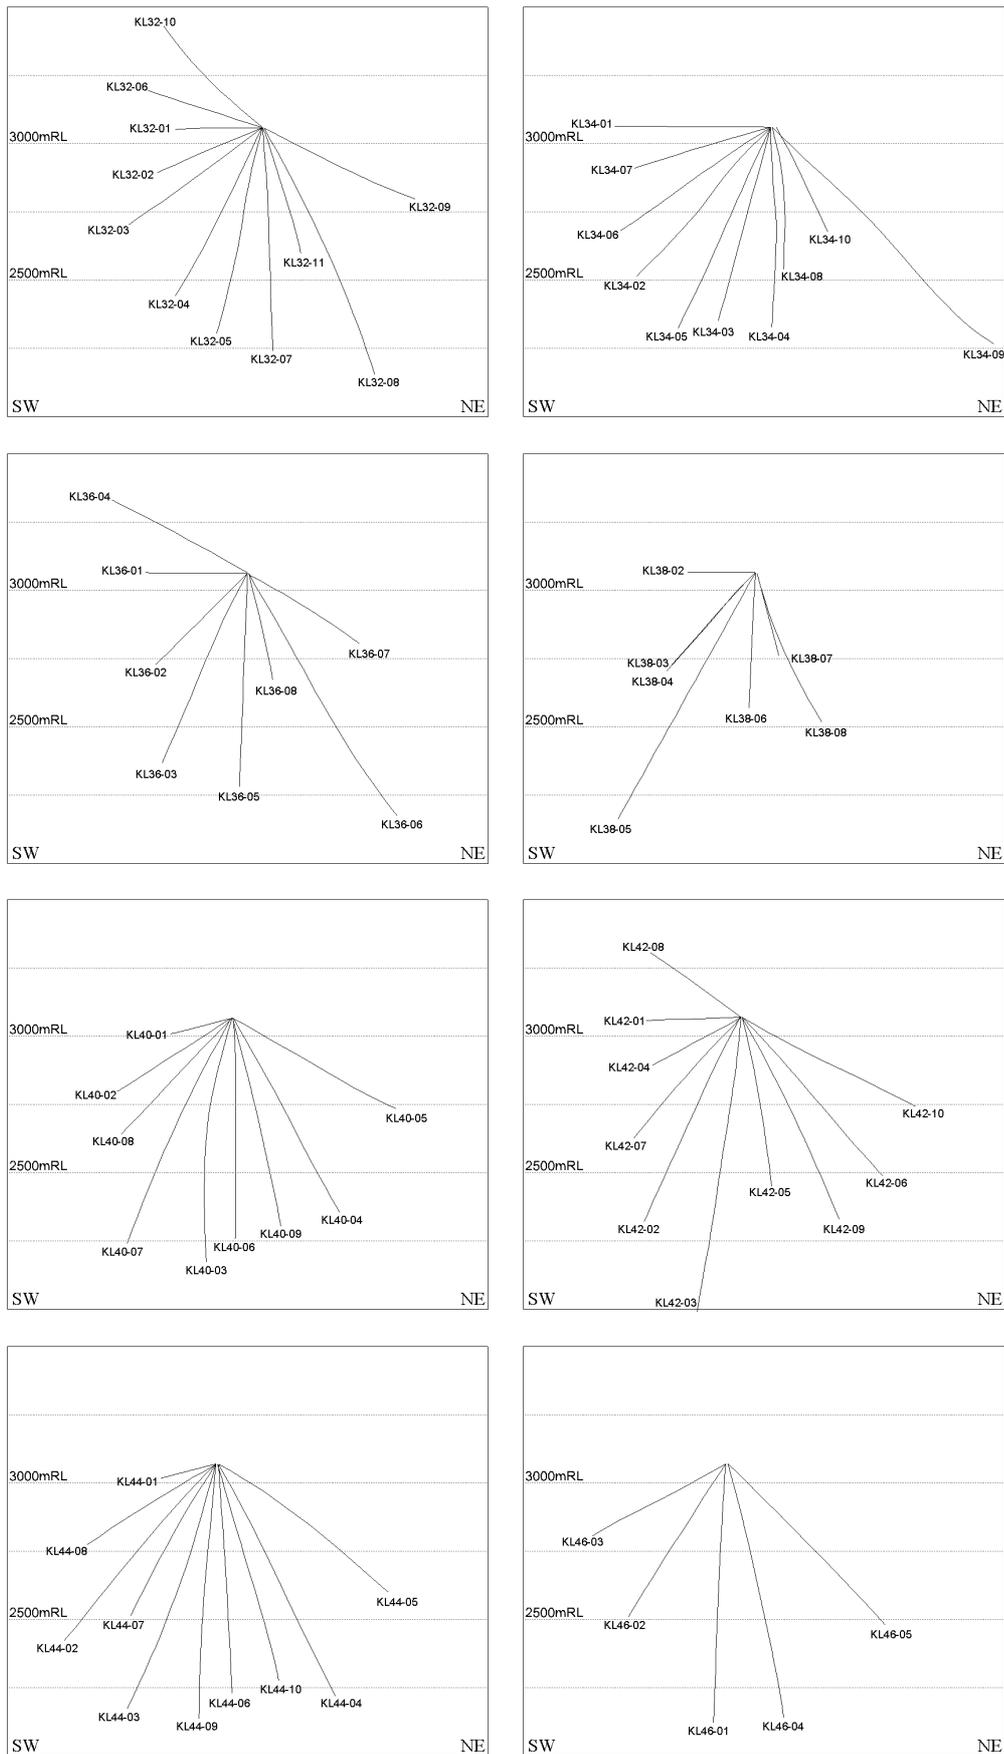

2 Host rocks

This section documents the wall rocks hosting Kucing Liar in terms of their composition and stratigraphical sequence. Each unit of the stratigraphic sequence is described in terms of lithology and internal sequence. The division of stratigraphy followed here is in line with that currently used within the mine environment by PT Freeport Indonesia. The rocks found in relatively unaltered sequences were compared to distinctive samples from the main mineralised zone in order to determine the reliability of textures observed in mineralised specimens for interpreting the stratigraphic position of individual samples (Chapter 4).

2.1 PREVIOUS WORK AND SOURCES OF DATA

2.1.1 Regional stratigraphic sequence

The stratigraphic sequence in the Ertsberg Mining District represents a continental margin including tidal, inner and outer shelf, plus deep marine sediments (Table 2-1). The Kembelangan Group is the lowermost stratigraphic package and comprises thick monotonous accumulations of shale and sandstone deposited in dominantly marine conditions from middle Jurassic to late Cretaceous times (Pennington, 1995; Quarles van Ufford, 1996). Contacts with both the underlying terrestrial to shallow marine Tipuma Formation and the overlying marine New Guinea Limestone Group are described as conformable (Pennington, 1995; Quarles van Ufford, 1996). The overall thickness of the Kembelangan Group is cited as 4,600m ± 1000 (Quarles van Ufford, 1996), while Pennington (1995) indicates that although the exposed thickness along the road exceeds 3,400m, the actual thickness is only 1,900m. The discrepancy is thought to be the result of tectonic thickening. The Kembelangan Group is subdivided into four formations, namely, the Kopai Formation, Woniwogi Sandstone, Pinya Mudstone and Ekmai Sandstone. Internal contacts have been described as conformable to disconformable by Quarles van Ufford (1996) but as conformable by Pennington (1995). In this study only the uppermost unit of this group, the Ekmai Sandstone, is significant. It is ~600m thick and is constrained by fossil evidence to a middle-upper Cretaceous age though it may possibly extend into the Palaeocene (Pennington, 1995; Quarles van Ufford, 1996). The upper Ekmai Sandstone is a 120m thick carbonaceous limestone referred to by mine geologists as the Ekmai Limestone, which includes an uppermost layer referred to as the Ekmai shale. Neither of these units was differentiated by Pennington (1995) or Quarles van Ufford (1996) but they are included on local geological maps (Parris, 1994).

The New Guinea Limestone Group conformably overlies the Kembelangan Group, is unconformably overlain by Quaternary glacial sediments and is documented as being 1,600-1,800m thick (Pennington, 1995; Quarles van Ufford, 1996). The sequence defines a regressive-transgressive-regressive sequence indicated by lower and upper platform carbonates separated by

fluvial and tidal facies sediments. The New Guinea Limestone group is subdivided into the Waripi Limestone, Faumai Limestone, Sirga Sandstone and Kais Limestone which were deposited on a stable carbonate platform marine over a ~50Ma period from latest Cretaceous to middle Miocene times (Quarles van Ufford, 1996). The Waripi Limestone is described as being 250-300m thick and is assigned a Palaeocene to early Eocene age (Pennington, 1995). The presence of anhydrite nodules within this unit indicates emergent conditions and supratidal environments. The upper contact with the overlying Faumai Limestone is described as conformable and gradational while the lower contact with the Ekmai Limestone may be disconformable (Pennington, 1995). The Faumai Limestone is distinguished from the Waripi Limestone by the presence of foraminifera and by the lack of sandstone (Table 2-1). The lower contact is conformable with the Waripi Limestone while the upper contact with the Sirga Sandstone is unconformable (Pennington, 1995), though evidence of prolonged exposure of the unit was not found (Quarles van Ufford, 1996). The Sirga Sandstone is a transgressive sequence of fluvial or near-shore sandstones including some organic-rich beds. The uppermost Kais Limestone is further subdivided into separate members, referred to by mine geologists as Tk1, Tk2, Tk3 and Tk4 (Parris, 1994). Although the top of the Kais Limestone is not exposed, the unit is at least 1,100m thick (Quarles van Ufford, 1996). It is distinct in the district as having a unique texture derived from tightly packed, large and elongate foraminifera. The lower contact with the Sirga Sandstone is conformable, while the upper contact is an erosional unconformity.

Table 2-1 Descriptions of stratigraphy in the Ertzberg Mining District

Formation	Lithology	Depositional environment
Kais Limestone (Tngk) 1,100 – 1,300m	Red algal, benthic foraminiferal limestone to packstone at the base, well developed bedding but internally massive. Massive, fossiliferous marls layers in lower sections.	Restricted shallow-marine carbonate platform sheltered from open marine currents
Sirga Sandstone (Tngs) 40m	Fining-upwards trough and tabular cross stratified quartz arenite, reworked foraminifera, coal and plant-rich seams.	Transgressive from terrestrial to shallow-marine and subaerial exposure, fluvial or nearshore unidirectional depositional current
Faumai Limestone (Tngf) 200 – 300m	Benthic foraminiferal limestone and packstone, 10m thick sandstone in lower and middle sections, occasional dolomite.	Shallow marine carbonate platform, restricted medium-energy
Waripi Limestone (Tngw) 250 – 400m	Sucrosic dolostone, quartz arenite sandstone and 2m thick nodular anhydrite-bearing beds.	Transitional from siliciclastic to carbonate, high energy shallow-marine shelf
Ekmai Sandstone (Kkes) 650m / 600m	Variably grain-sized quartz arenite with trough and tabular cross-bedding, upper 90m is mudstone and limestone.	Shallow shelf, nearshore to possible beach facies, the upper limestone is outer-shelf to slope
Pinya Mudstone (Kp) 1550m / 600m	Laminated massive mud and siltstone interbedded with 20cm thick well-sorted and fine-grained sandstone.	Shelf margin and slope during transgression, storm generated sands and fair weather mud.
Woniwogi Sandstone (Kw) 1000m / ~300m	Poorly-sorted coarse-grained to granule sandstone overlain by well-sorted fine to medium-grained sandstone, sporadic cross-bedding but generally massive; belemnites.	Shallow marine and slope from sand-rich shelf, basal section is either beach or debris flows
Kopai Formation (Kkp) 1400m / 300m	sandstone, siltstone/mudstone and subordinate limestone; crinoids, echinoderm and ammonite.	Transitional fluvial to nearshore marine, shallow shelf, distal shelf or slope. Lower sections are transgressive, upper sections are regressive

Source: Pennington (1995) and Quarles van Ufford (1996). The numbers below the unit names refer to their thicknesses. There is a consistent discrepancy between local and district studies where larger values are reported from regional studies.

2.1.2 District outcrop and deep drilling

There are numerous spectacular large-scale exposures of the Kucing Liar host stratigraphy in the district (e.g. Plate 2-1). The most visible differences in the stratigraphic units are the relative thicknesses of beds and the effects of erosion (Plate 2-1). The Ekmai Sandstone situated at the base of the mineralised sequence is very thickly bedded at a scale of tens of metres. By contrast, the overlying Waripi and Faumai Limestone units are very thinly bedded. A major topographic break occurs at the upper contact of the Ekmai Sandstone, which is suspected to be due to mechanical contrasts between the thick sandstone and thinner limestone, possibly exacerbated by the presence of the carbonaceous Ekmai Limestone. The contact of this unit with the underlying sandstone is very deeply eroded relative to overlying and underlying units in the walls of the Aghawagon Valley (Plate 2-1). Topographic breaks in the stratigraphic pile are consistent across the district and are situated at changes from sandstone to limestone or shale (Plate 2-1). These breaks have been used as marker horizons during district-scale geological mapping in defining the position of stratigraphic contacts (P. Manning, *pers comm.*). The extremely rugged nature of outcrop in the Ertsberg Mining District makes it logistically difficult to investigate. Consequently, analysis of strata intersected by exploration drilling at the margins of the Grasberg Igneous Complex (Figure 2-1) has provided details of the composition, texture and sequence of the Kucing Liar host sequence.

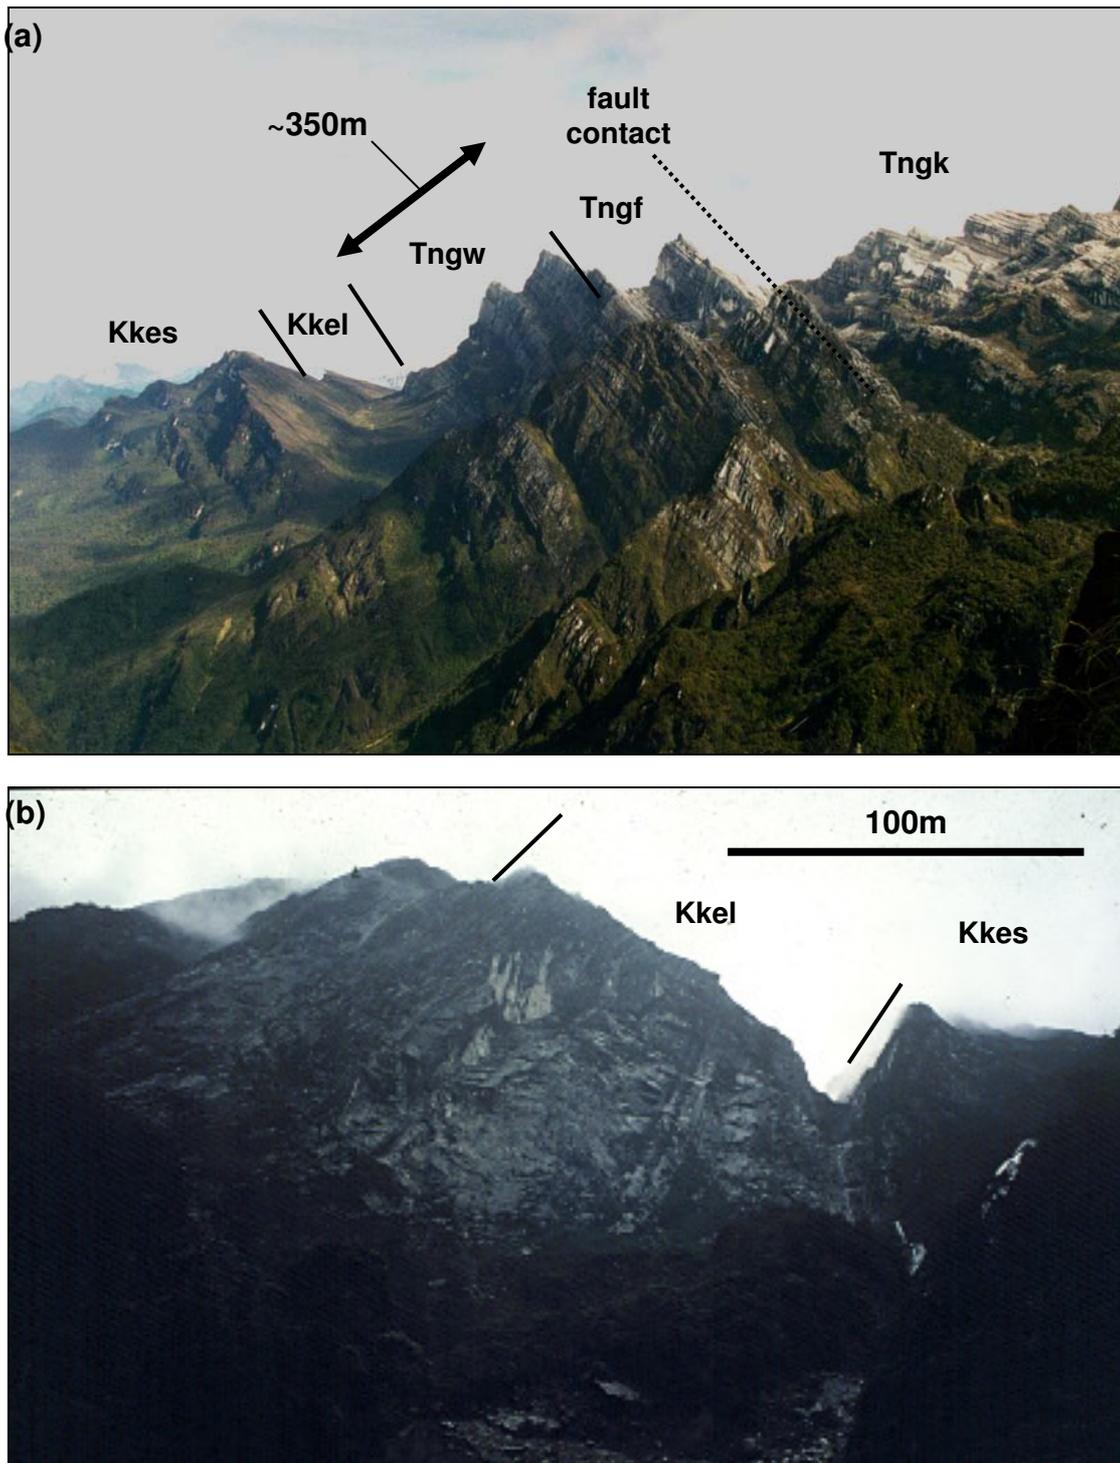


Plate 2-1 Large-scale exposure of host stratigraphy

(a) View west from north of Wanagon along strike showing a continuous section of stratigraphy. Breaks in topography are related to lithology, the most prominent occurring at the transition from Ekmai Sandstone (Kkes) to Ekmai Limestone (Kkel). Topographic breaks reflect visible changes in the bedding scale, which is small for the Waripi (Tngw), Faumai (Tngf) and Kais (Tngk) limestone units and much larger for the Ekmai Sandstone. The different dip of Kais Limestone to the right is probably due to faulting. (b) A view of the east wall in a valley where the mill is situated illustrates deep weathering of the Ekmai Limestone and a close up view of the thinly bedded Waripi Limestone.

Drilling conducted on the north and northwest margins of the Grasberg Igneous Complex intersected reasonably coherent stratigraphy equivalent to the host rocks at Kucing Liar. Mine staff identified the major stratigraphic packages and the contact characteristics prior to this study. Two drill holes, KLS1-1 (total depth 2199m) and KLS3-1 (total depth 2235m) completed in the course of district exploration intersected less altered equivalents of the Kucing Liar sequence, respectively northeast (northern limb of Yellow Valley Syncline) and northwest (axis of Yellow Valley Syncline) of the Grasberg Intrusive Complex (Figure 2-1). Drill hole KLS3-1 is near vertical and is expected to record true thicknesses of stratigraphic units as the stratigraphic layering should be near horizontal in the axis of the syncline. These two drill holes intersect the least altered host rocks available but nevertheless contain locally significant alteration. Although KLS3-1 was collared in the Grasberg Igneous Complex it intersected sedimentary units at 200m depth due to the flaring outwards of the igneous-sediment contact. No igneous bodies were intersected at depth in either of these drill holes. Drill hole KLS1-1 ended some 200m into the Ekmai Sandstone, while KLS3-1 intersected only the top 75m of the unit. KLS1-1 and KLS3-1 were both sampled for this study from the base of the Kais Limestone to the top of the Ekmai Sandstone at roughly 10m intervals, or less where significant changes in lithology were observed. Samples were collected from these two drill holes for petrographic examination and characterisation. Stained thin sections were produced to determine carbonate compositions of each sample. Details of the procedure are recorded in Appendix II. Carbonate composition is revealed in the colour imposed on the grains and matrix by staining. Dolomite is colourless to blue, while calcite is pink to purple. In each case, the darker colours are due to the presence of iron. Discrimination of calcite, dolomite, ferroan dolomite and ferroan calcite is possible from this technique. Thin sections were used to collect information specifically relating to:

- grain composition, size and abundance,
- matrix composition, grain size and abundance, and
- carbonate composition.

Identification of foraminifera for the of the Faumai, Sirga and Kais units was facilitated by a report completed by the Palaeontology and Stratigraphy Division of the Geological Research and Development Centre, Directorate General of Geology and Mineral Resources, Department of Mines and Energy in Bandung, West Java (GRDC, 1999). Stratigraphic columns for each of the drill holes were created from the data recorded in thin section descriptions, allowing correlation of the major stratigraphic features (Figure 2-2).

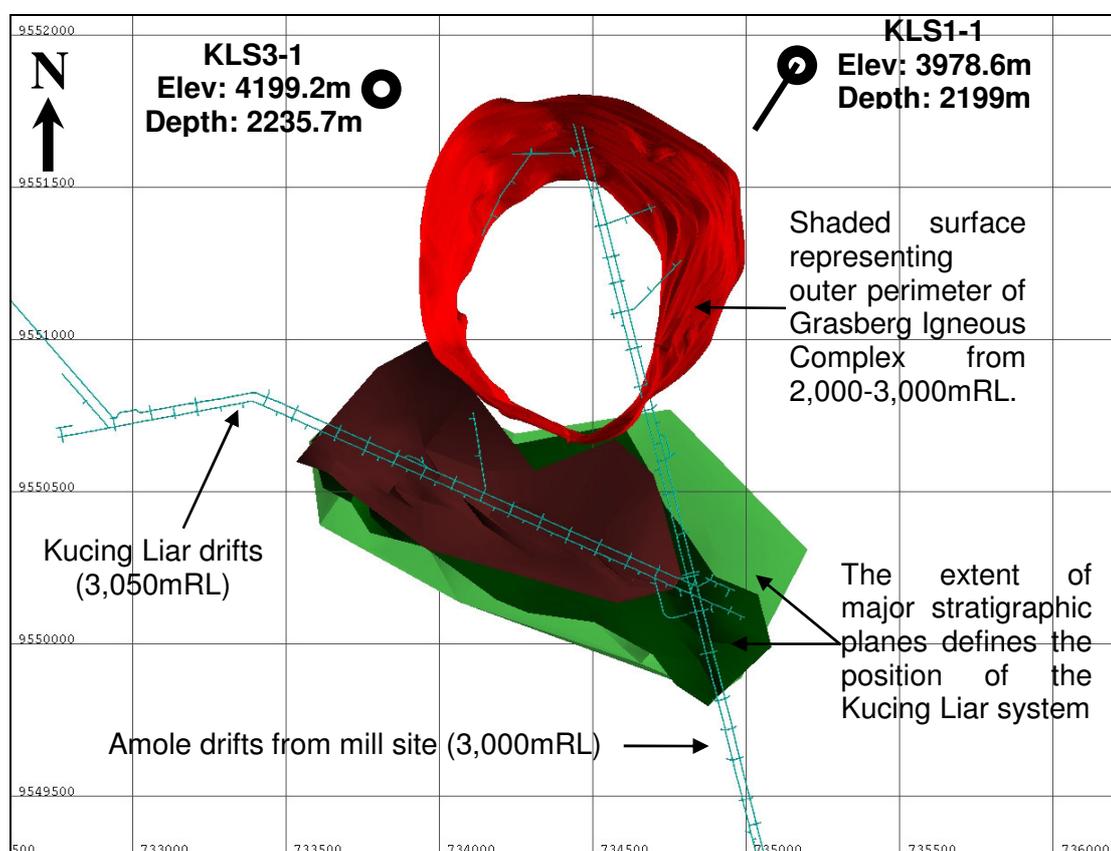


Figure 2-1 Plan projection showing collar locations for stratigraphical drillholes

Positions of KLS1-1 and KLS3-1 with reference to the location of Grasberg and Kucing Liar. KLS3-1 is vertical to the end of hole; KLS1-1 is vertical to 600m, then dips -60° toward southwest then is near vertical again from 900m. The section of KLS1-1 sampled for this study (870-2,200m) is oriented at -60° toward 213° . Grid spacing is 500m.

2.2 RESULTS

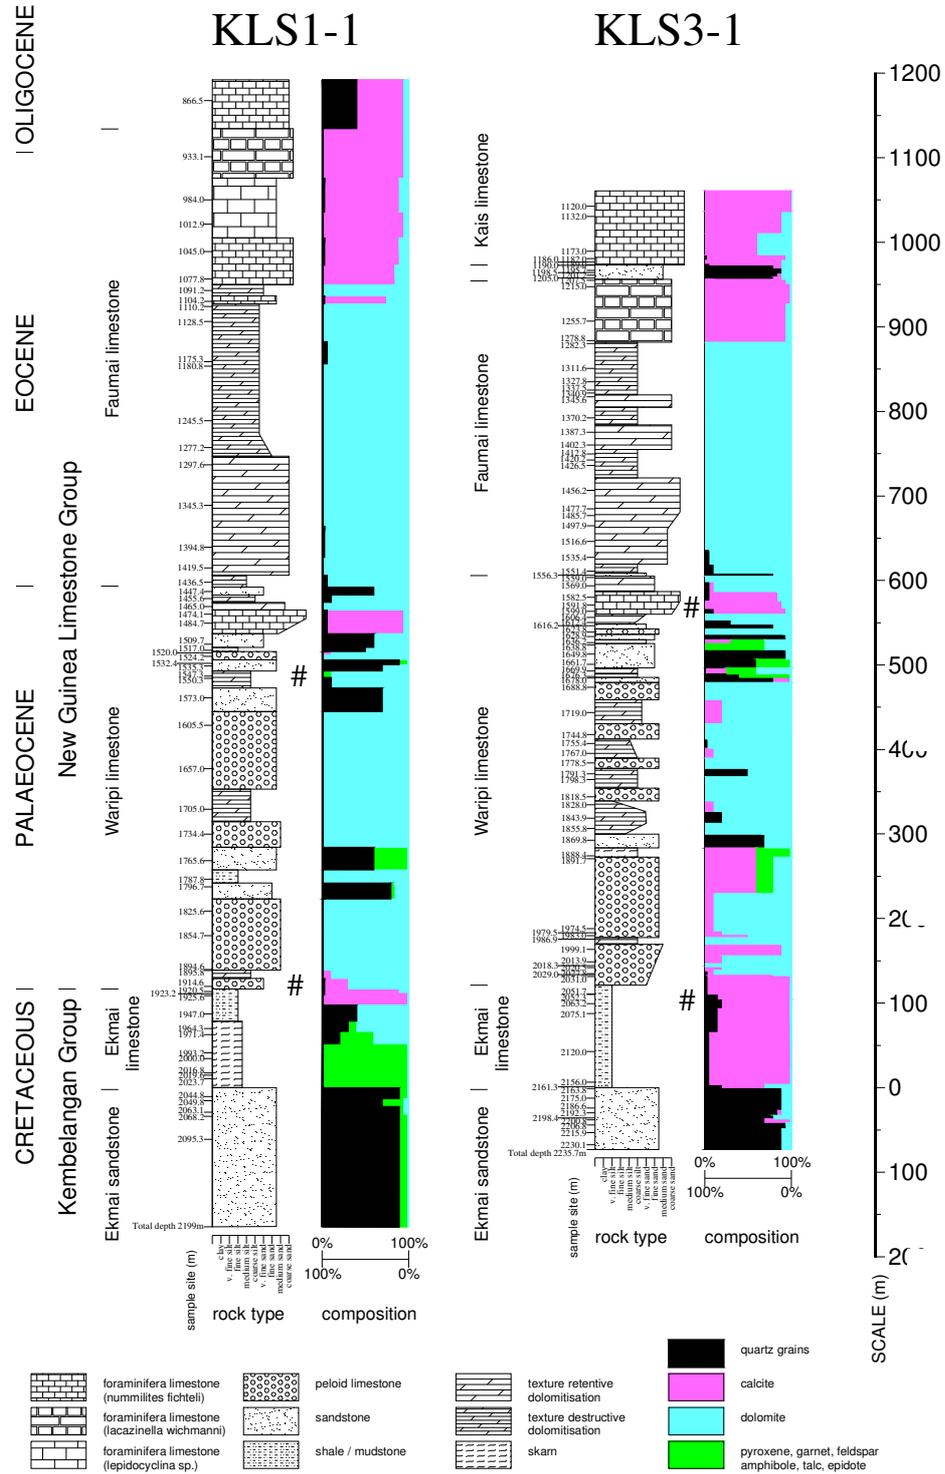


Figure 2-2 Lithology and composition of unmineralised stratigraphy

Sample locations from KLS1-1 and KLS3-1 for lithology descriptions are shown on the left of each column and marked by a tick and the depth. Different apparent thickness of the Faunai Limestone is due to variable intersection angles. Ages from Pennington (1995) and Quarles van Ufford (1996). Hatch symbols indicate presence of anhydrite nodules.

2.2.1 Descriptions of local unaltered lithological sequences

Kembelangan Group – Ekmai Sandstone (Kkes)

The Ekmai Sandstone is the lowermost unit intersected in Kucing Liar drilling. Its base was not intersected in either drill hole KLS1-1, which penetrated 170m, or in KLS3-1, which penetrated only 75m (Figure 2-2). The unit is largely homogeneous and consists of 80-90% very well sorted, angular to subangular quartz grains of 0.3mm grainsize and rare complete foraminifer (Plate 2-2a). However, there are also minor layers of red sandstone and coarse-grained bioclast-bearing sandstone (Plate 2-2b). The Ekmai Sandstone is thickly bedded (~50-100m) and bedding planes that are visible in large-scale exposures (Plate 2-1) are not recognisable in drill core. The overlying contact with the Ekmai Limestone is defined by disappearance of quartz grains (Figure 2-2).

Kembelangan Group – Ekmai Limestone (Kkel)

The Ekmai Limestone is 120m thick in KLS3-1 where it is almost pristine, while the intersection in KLS1-1 is altered to pyroxene-feldspar-garnet-epidote. The predominant lithology is very fine-grained black micritic limestone with a significant shale component containing up to 20% quartz and bioclasts. The base of the unit contains apparent bioturbation textures (Plate 2-2c). The limestone changes from massive and shaly in the lower sections, to fissile in the middle (Plate 2-2d), and bioclastic near the top (Plate 2-2e). A distinct layer (~5m) of black shale at the top of the Ekmai Limestone is locally referred to as the Ekmai shale.

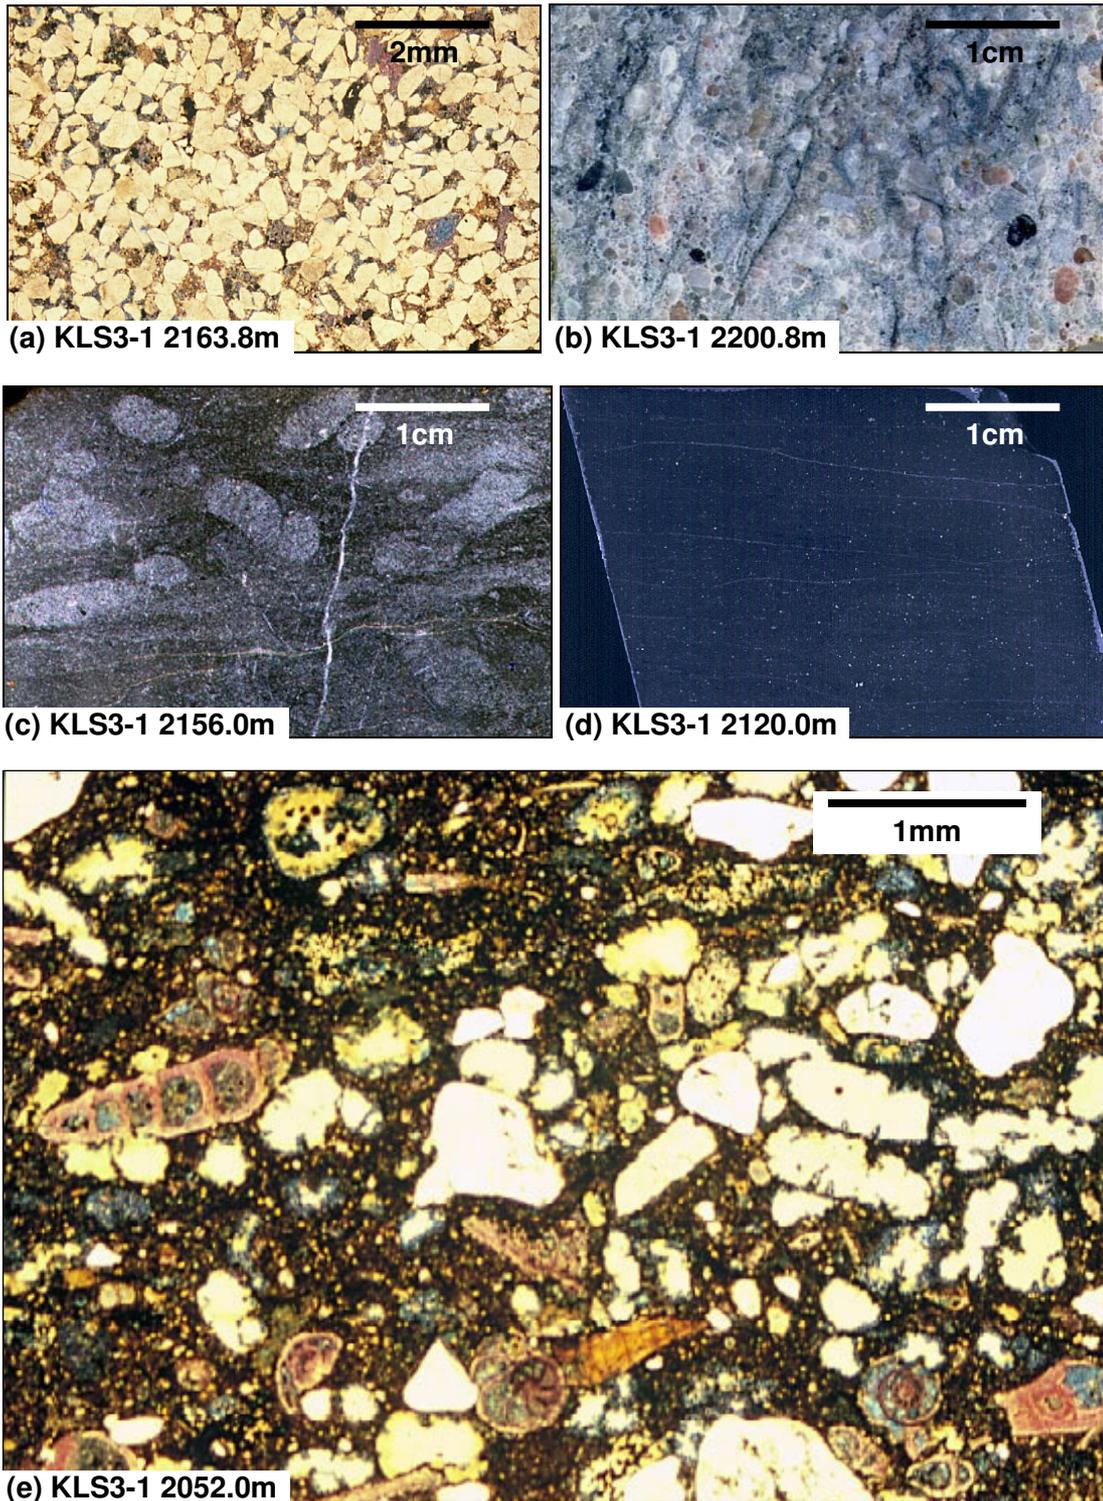


Plate 2-2 Examples of Ekmai Sandstone and limestone

(a) Photomicrograph of typical Ekmai Sandstone at the top of the unit, stained for carbonate composition. A grain (right) stained blue (ferroan dolomite) and pink (calcite) is a foraminifer. Plane light (b) Coarse-grained sand and carbonate layer (<5m) near top of Ekmai Sandstone. (c) Pale grey patches of sand grains in shale/limestone from the lower Ekmai Limestone that may be burrows. (d) Fissile shale from the middle of the Ekmai Limestone. (e) Coarse-grained texture of sand and bioclasts in a shale matrix of the upper Ekmai Limestone. Plane light image of a stained section.

New Guinea Limestone Group – Waripi Limestone (Tngw)

The Waripi Limestone is approximately 430m thick in KLS3-1, which is significantly more than the ~250m indicated by district studies (Pennington, 1995; Quarles van Ufford, 1996). It is dominated by peloid limestone but contains significant layers of sandstone, plus subordinate foraminiferal limestone and shale. The unit has been extensively dolomitised in both KLS1-1 and KLS3-1, although some samples containing primary calcite were collected. Exposed sections of the Waripi Limestone have very well defined sub-metre scale bedding structures (Plate 2-3).



Plate 2-3 Outcrop of the Waripi Limestone

Layers of dolomite in outcrop of the section measured by mine staff near the Waripi Limestone-Faumai Limestone contact to the north of the Wanagon sill outcrop.

Grey peloid limestone/dolostone (Plate 2-4a) forms sections up to 180 thick in the Waripi Limestone (Figure 2-2). Peloid grains are spherical, micritic, possess no internal structure and constitute 60-80% of the rock. Peloid grain size varies from 0.1 to 0.6mm but averages 0.3mm. Where peloid limestone is not dolomitised, the grains and matrix are composed of micritic calcite.

There are three sandstone members within the Waripi Limestone that are used as marker horizons. A 10-30m layer in the middle Waripi Limestone separates two thick sequences of peloid

limestone/dolostone (Figure 2-2). The grains in this member are well sorted, angular to subangular, vary from 20-80% total content and average 0.3mm in size. A 50m (plus subordinate dolostone/limestone) member near the top of the Waripi Limestone is composed of 60-90% moderately sorted, angular to subangular quartz grains of 0.2mm average grainsize, increasing to 0.4-0.6mm at the base of the member. A third 5m-thick laminated sandstone member with well sorted, angular to sub-angular, 30-80% sand grains of 0.1mm average size, has been used to mark the upper contact of the Waripi Limestone (Figure 2-2, Plate 2-4e). In all cases the matrix is composed of micritic calcite or dolomite spar. Talc, tremolite and pyroxene are commonly present in the matrix of sandstones in both KLS1-1 and KLS3-1 and impart on what is normally grey sandstone a pasty white appearance (Plate 2-4b). A shale horizon approximately 5m thick was identified and sampled in KLS3-1 in the upper Waripi Limestone at the top of the upper sandstone layer (Figure 2-2). This layer was not identified in KLS1-1. Another shale layer was identified in drill hole KLS1-1 within the middle sandstone layers (Figure 2-2). A 60-80m horizon of limestone containing elongate to rounded foraminifera is present in the upper Waripi Limestone, bound top and bottom by sandstone (Figure 2-2). The foraminifera vary from 1-5mm in size, and constitute 50-80% of the rock (Plate 2-4d). Dolomite, anhydrite and native sulphur have replaced foraminifer grains in places where dolomitisation is prevalent in the matrix (Plate 2-8). These foraminifera are similar in size and shape to vughs in dolostone of the lower and middle Faumai Limestone that are usually infilled with dolomite quartz, anhydrite and native sulphur. Anhydrite nodules occur at three specific levels in the Waripi Limestone in KLS3-1, namely at the top between two sandstones, in the middle of the unit associated with sandstone and shale, and in a narrow band (~20m) near the base of the unit. They vary in shape from spherical to lenticular and are roughly elongate in direction of bedding (Plate 2-4c). Nodule size varies from <5mm to 50mm. The nodules at the base are the more spherical type.

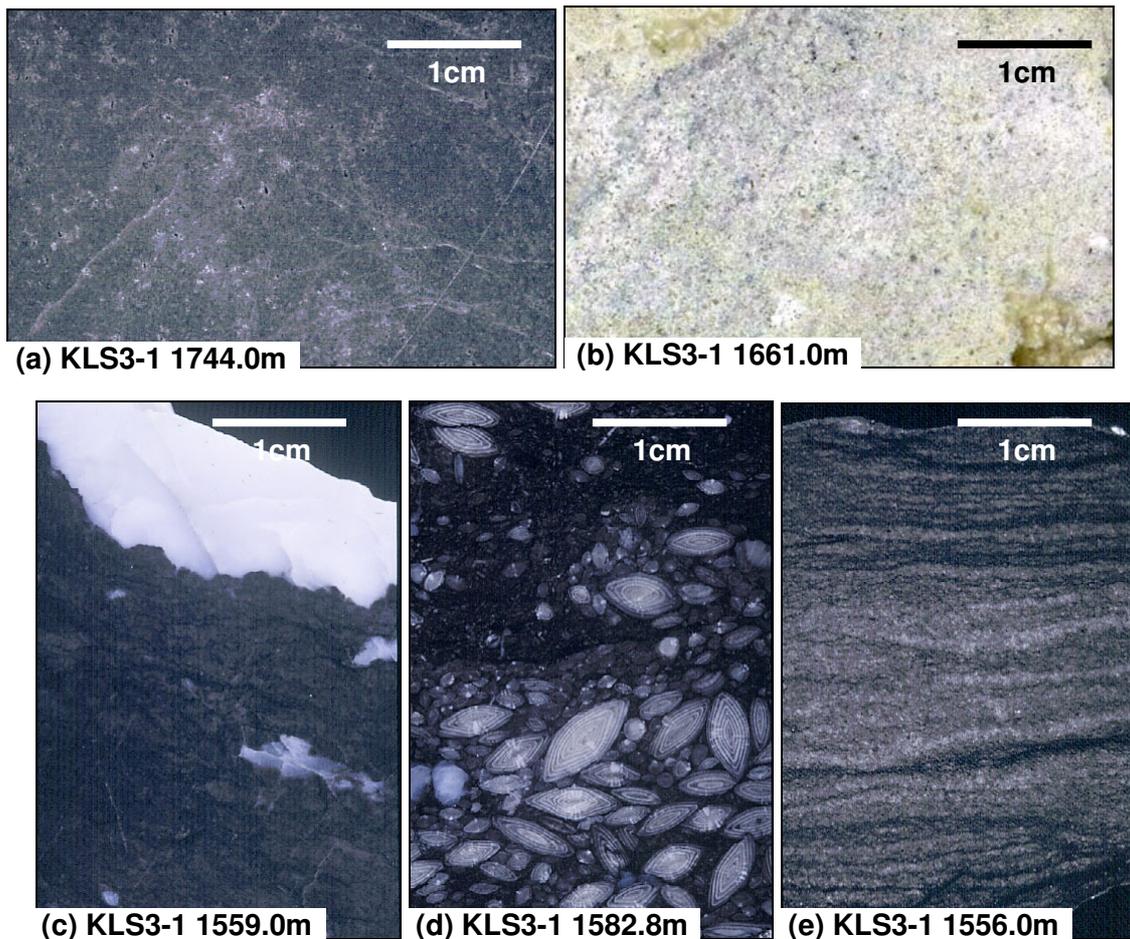


Plate 2-4 Examples of Waripi Limestone visible textures

(a) Medium grey peloid dolostone typical of the majority of the Waripi Limestone. The lines are fractures associated with lighter grey dolomite alteration. (b) Sandstone matrix that is normally dark grey is changed to white due to presence of amphibole-pyroxene-talc. (c) An anhydrite nodule from the upper Waripi Limestone oriented subparallel to sedimentary layering. (d) Foraminifera from the upper Waripi Limestone which resembles texture in the middle Faumai Limestone where leached holes have been infilled with coarse-grained carbonate. (e) Finely laminated sandstone that marks the upper contact of the Waripi Limestone.

New Guinea Limestone Group – Faumai Limestone (Tngf)

The Faumai Limestone is 350m thick in KLS3-1. The lower half of the Faumai Limestone is extensively dolomitised in both KLS1-1 & KLS3-1 and the only unaffected parts occur at the top of the unit (Figure 2-2). Identifiable Faumai Limestone in KLS1-1 and KLS3-1 consists of fossiliferous calcite limestone, dolomitised limestone and dolostone. Distinctive round foraminifer *lacazinella wichmanni* (Plate 2-5a and Plate 2-5c) dominate the uppermost limestones that are composed of uniform packstone, in which the foraminifer grains range from 1-2mm in

diameter. A micritic calcite matrix supports the foraminifer grains that constitute up to 80% of the rock. This member is approximately 70m thick in KLS3-1. Below this in KLS1-1, there is another preserved limestone member containing a variety of carbonate grains. In this member the elongate foraminifer *lepidocyclina sp.* is common (Plate 2-5b). Also included in these upper layers are subordinate grains of echinoderms, bryozoa and coralline algae.

New Guinea Limestone Group – Sirga Sandstone (Tngs)

The thickness of the Sirga Sandstone intersected in drill hole KLS3-1 is approximately 20m. It unconformably overlies the Faumai Limestone and consists of a series of interbedded sandstones and fossiliferous carbonate rocks (Plate 2-6). The dominant carbonate is calcite, although dolomite is present in minor quantities. There are ~5m beds in the Sirga Sandstone with very high organic contents. The Kais-Sirga contact appears conformable, as a section at the top of the Sirga Sandstone contains 50% quartz grains and 50% foraminiferal grains of same species present in overlying limestone.

New Guinea Limestone Group – Kais Limestone (Tngk)

The original thickness of the Kais Limestone is not known as the top of the unit has an unconformable contact with Quaternary sediments. Only the lower part of the Kais Limestone has been examined in this study as upper sections do not host Kucing Liar mineralisation. The base is typified by limestone with packed elongate foraminifera up to 10mm long (Plate 2-7). These are dominantly *nummulite fichteli* plus minor amounts of *operculina sp.*, and *operculinella*. Minor dolomite and scattered quartz grains are present in samples collected from the lower Kais Limestone.

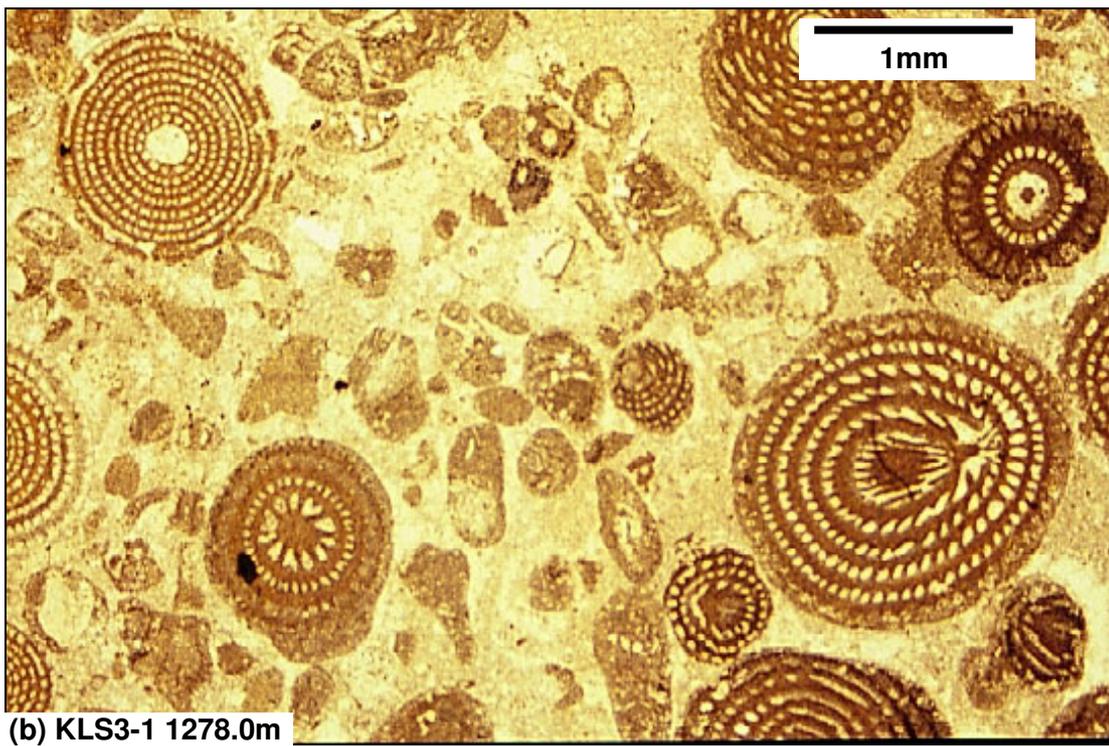
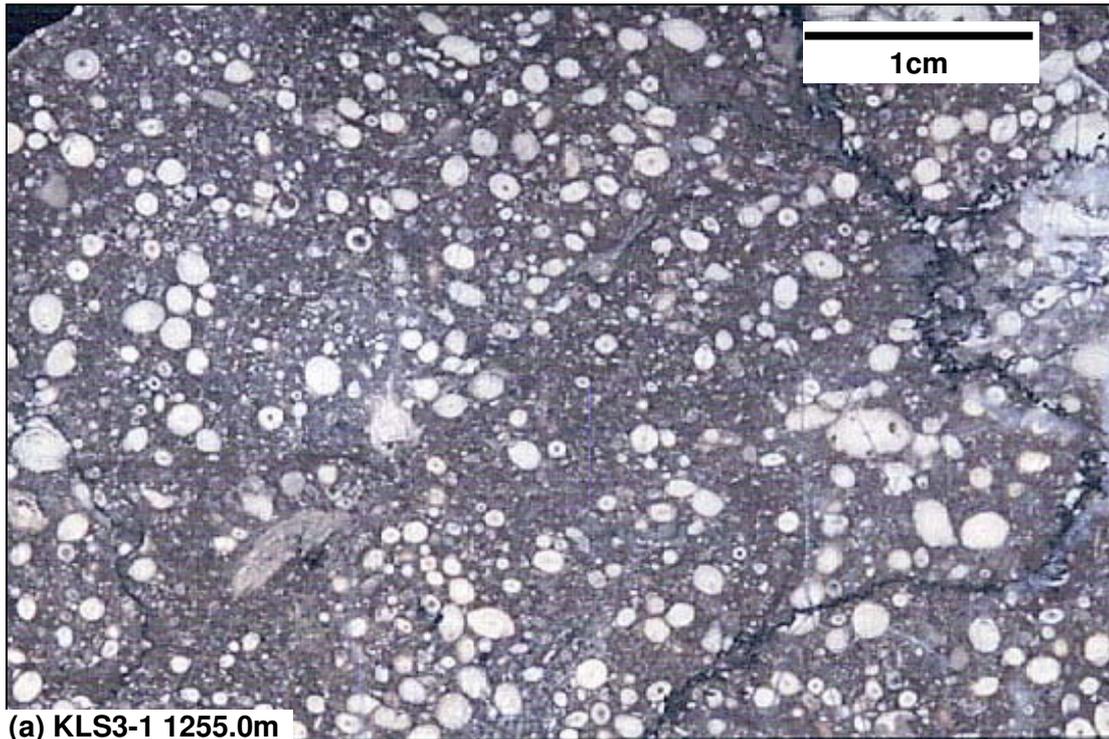


Plate 2-5 Examples of Faunai Limestone visible and micro-textures

(a) Distinctive round foraminifera (*Lacazinella wichmanni*) from the upper Faunai Limestone (b) Grains of *Lacazinella wichmanni* are calcite while the intervening matrix has been converted to dolomite. Plane light image of a stained section.

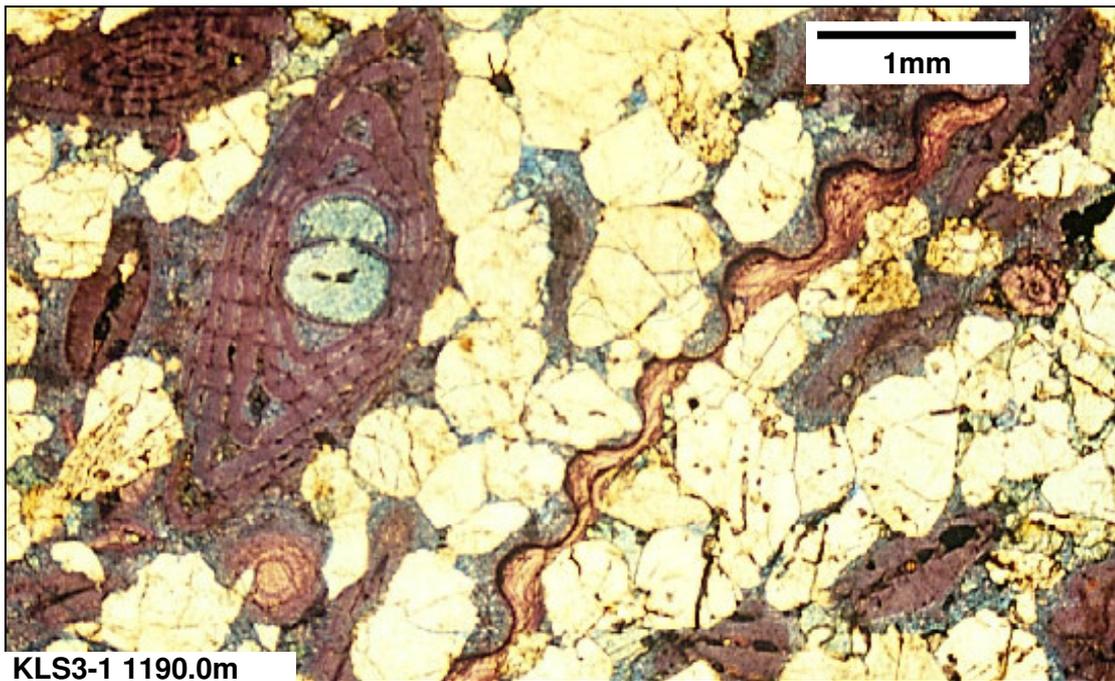


Plate 2-6 Example of Sirga Sandstone

Photomicrograph illustrating large nummulites fichteli identical to those in the overlying Kais Limestone mixed with coarse sand grains. Pink and purple colours indicate calcite while blue indicates dolomite. Plane light image of a stained section.

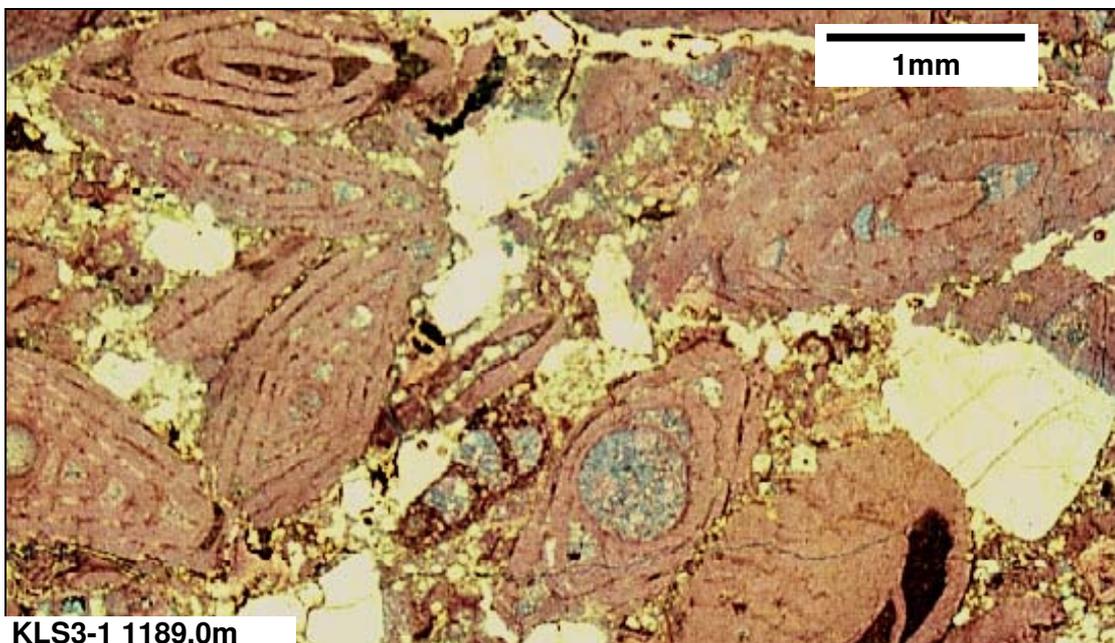


Plate 2-7 Example of Kais Limestone

Photomicrograph illustrating nummulites fichteli that dominate the lower Kais Limestone. Much smaller spiral-shaped operculina sp. is also present. Foraminifera are (pink) calcite while some have ferroan dolomite (blue) in the centre. The matrix between grains has been altered to dolomite (yellowish). The large white grains are quartz. Plane light image of a stained section.

2.2.2 Textures developed in low-intensity distal alteration

Dolomitisation

Samples from KLS1-1 and KLS3-1 indicate variable effects of dolomitisation (Plate 2-8) most common as well as calc-silicate alteration. The number of dolomitisation events and their extents are unknown, and their precise relationships to the mineralizing hydrothermal systems are also not clear. The effects of dolomitisation vary from minor alteration of grains and matrix resulting in the preservation of the original texture (Plate 2-9), to the complete replacement of original calcite by dolomite spar, resulting in the destruction of the original sedimentary texture. All textures between these two endmembers are represented. Complete replacement of calcite by dolomite occurs over very short distances as seen in composition columns for samples in KLS1-1 and KLS3-1 (Figure 2-2). The scale of replacement is less than the sample spacing of 10m as the change in carbonate is complete between two samples. Figure 2-2 also illustrates that calcite limestone is preserved near sandstone horizons at the top and bottom of the Faumai and Waripi Limestone units. A spatial association between texturally destructive dolomitisation and sandstone layers is apparent in KLS3-1. Contacts between unaltered limestone and texturally destructive dolostone range from gradational to sharp and a complete loss of sedimentary texture occurs over a 4m interval in KLS3-1 between 1278.8m and 1282.3m. Layers are discretely altered to equigranular dolomite sparite and are intercalated with dolostone where the original texture can be identified. Dolomitisation is most intensely developed in the limestone-only packages of these two units between sandstone horizons. Dolostone is grey in the Waripi Limestone (Plate 2-8a) and brownish-beige in the Faumai Limestone (Plate 2-8f). Spherical to elongate pores filled with anhydrite and dolomite (Plate 2-10) in the middle and lower parts of the Faumai Limestone are very similar in size, shape and abundance to similar features in foraminiferal limestone of the upper Waripi Limestone. The matrix in these rocks consists of subhedral to euhedral dolomite grains and the pores are filled to varying degrees with varying amounts of calcite, dolomite or native sulphur (Plate 2-8c, d & e).

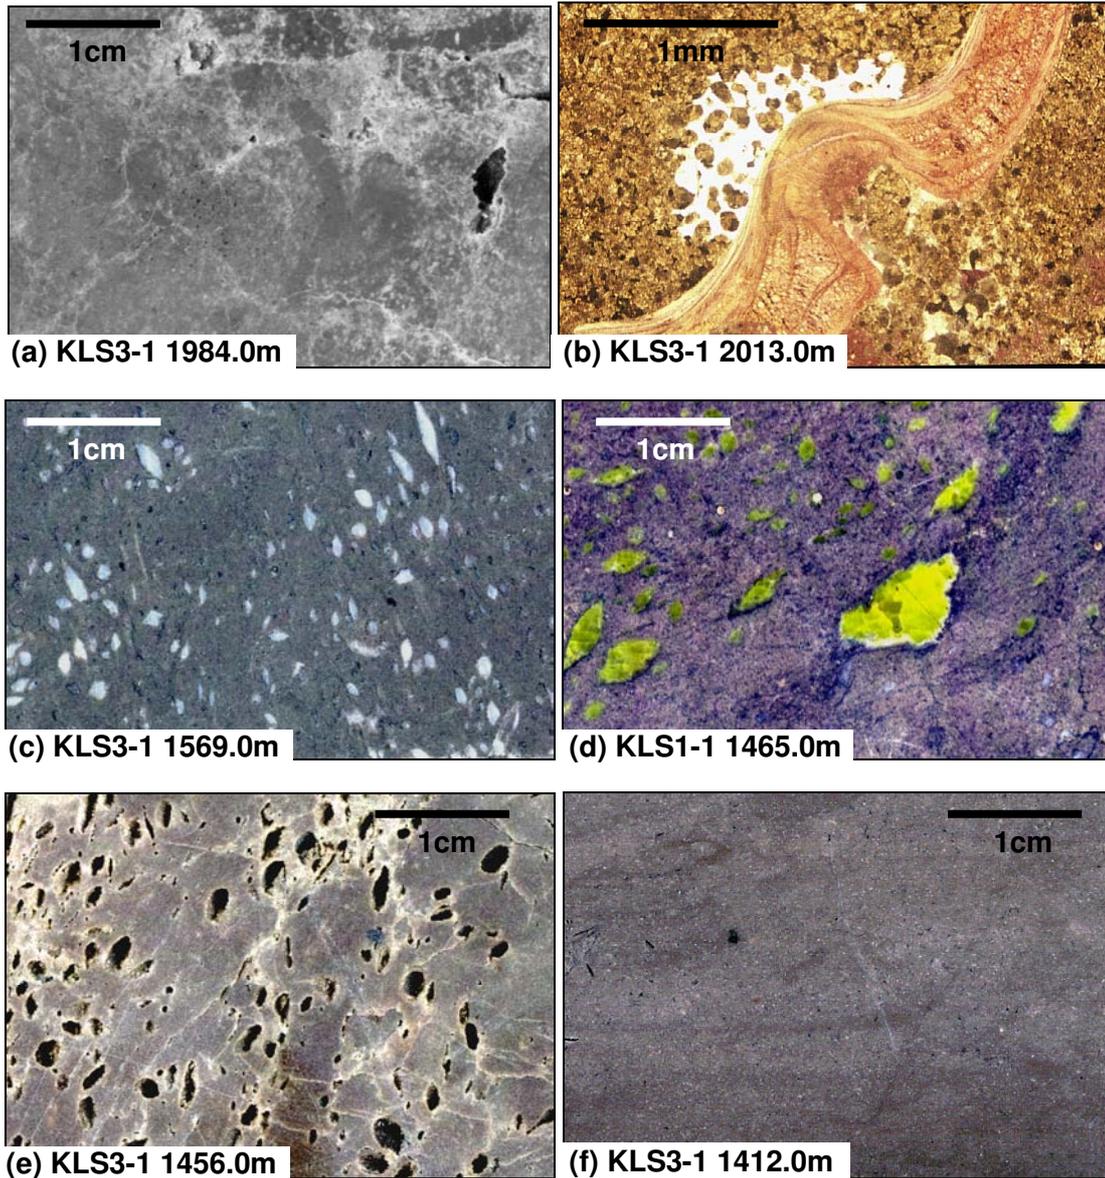


Plate 2-8 Examples of dolomitisation textures

(a) Fine-grained dolomitised peloid limestone such as is common in the Waripi Limestone. (b) An unidentified bioclast composed of original calcite is surrounded by a matrix of yellowish dolomite from the lower Waripi Limestone. The grey-white area in the view is a cavity. Plane light image of a stained section. (c) White anhydrite and dolomite infilling cavities that are shaped like foraminiferal grains from uppermost Waripi Limestone. (d) An example of the same limestone layer depicted in (c), though here the foraminifer-like voids are infilled with native sulphur (e) A sample from the lower Faumai Limestone believed to have been foraminiferal limestone where the fossil grains have been dissolved. The vughs are lined with quartz and/or dolomite. Note similarity with (c) above. (f) Intense dolomitisation results in complete destruction of clastic sedimentary textures in this dolomite sparite, although some semblance of the layering appears to be preserved as darker zones of dolomite in this sample from the middle Faumai Limestone.

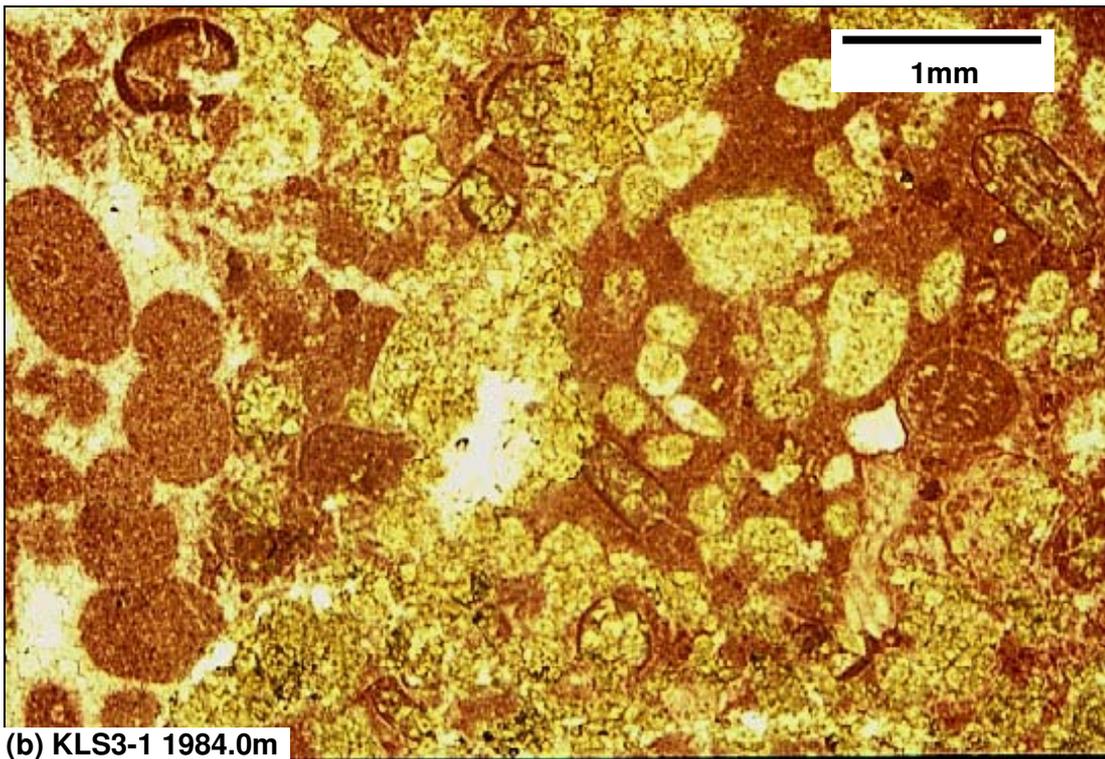
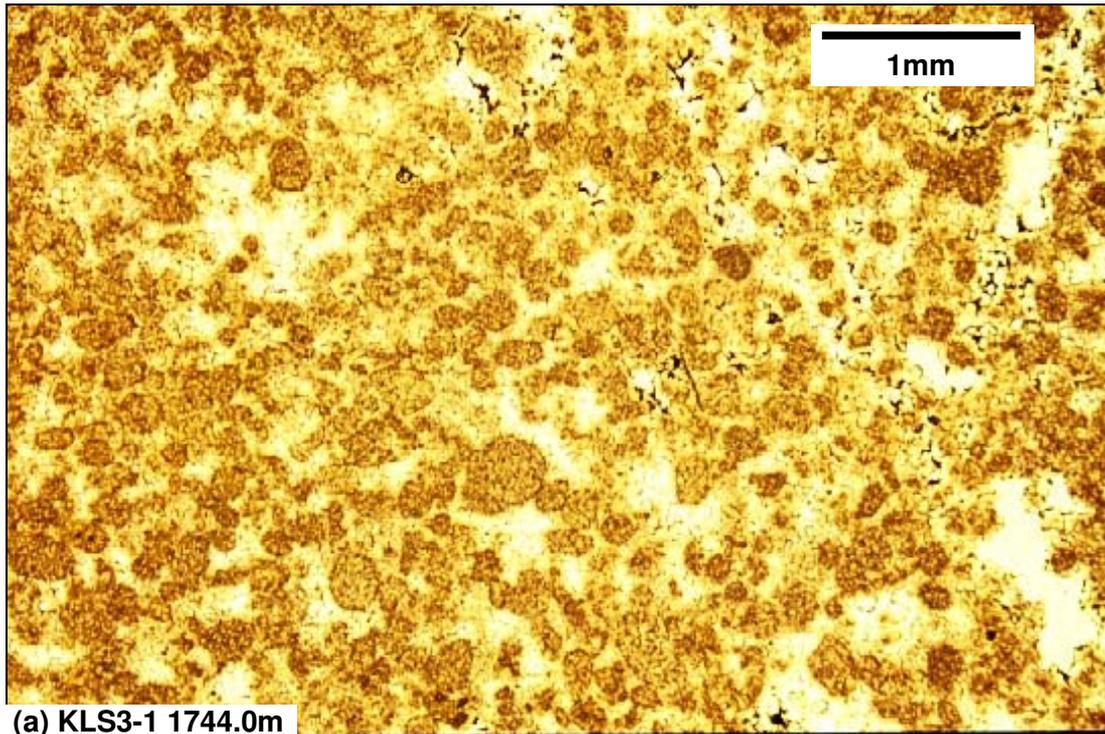


Plate 2-9 Examples of dolomitisation micro-textures in peloid limestone

(a) Yellowish dolomite surrounds reddish micritic calcite peloid grains and voids (white patches). Plane light image of a stained section (b) Micritic calcite peloid limestone replaced by two generations of dolomite. A yellowish-coloured type replaces the peloid grains at right and bottom, while a paler variety of dolomite preferentially affects matrix rather than the micritic grains and surrounds pores (white). Plane light image of a stained thin section.

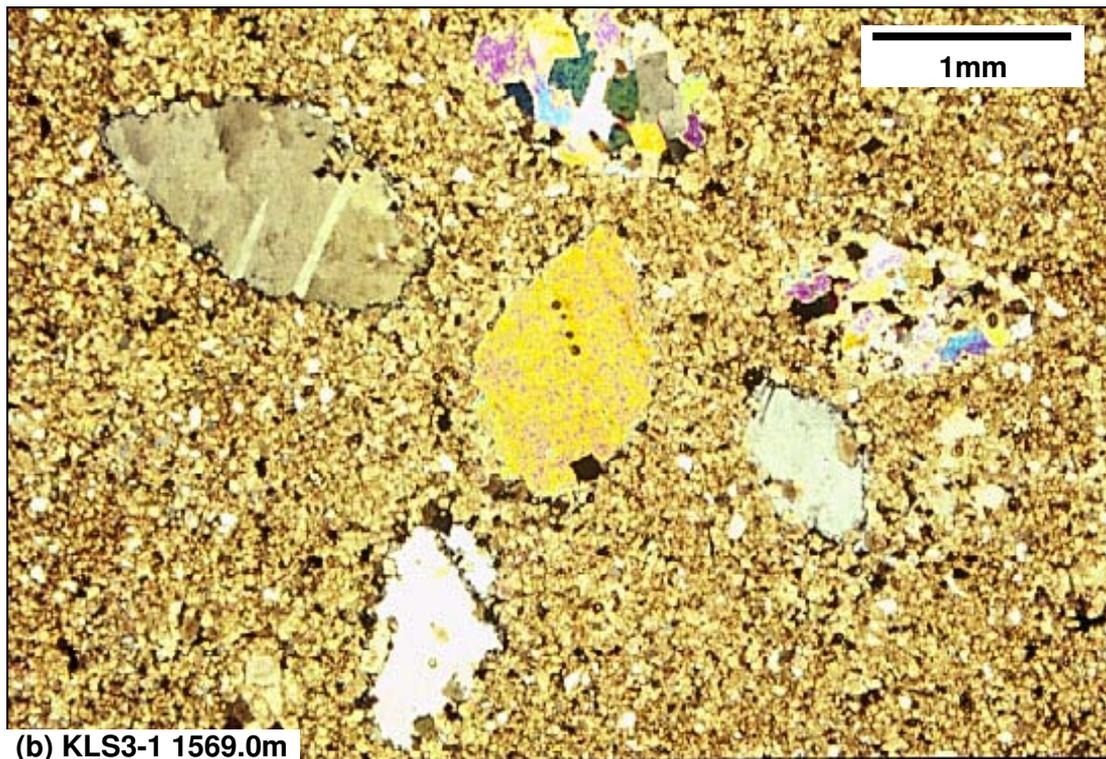
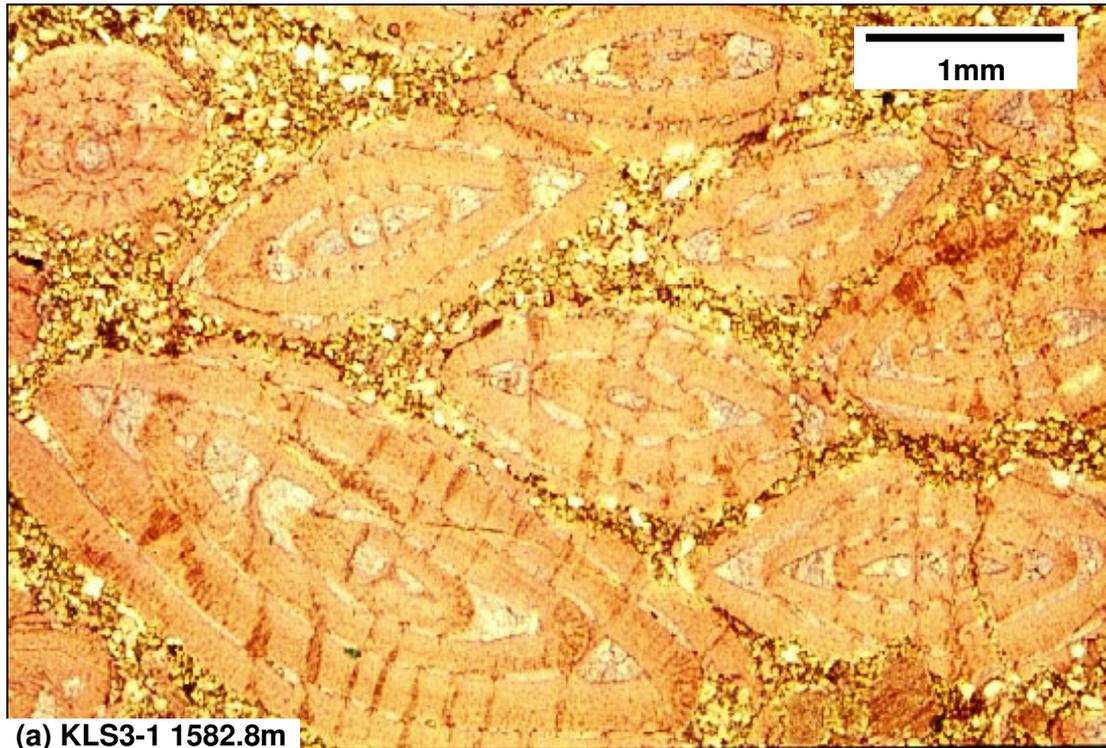


Plate 2-10 Examples of dolomitisation micro-textures in foraminiferal limestone

(a) Foraminifer grains composed of primary calcite surrounded by very fine-grained dolomite spar. Plane light image of a stained thin section. (b) Dolomite (high birefringence, twinned) and anhydrite (moderate birefringence, polycrystalline) infilling cavities that are of similar shape though much smaller than foraminifera illustrated in plate (a). Cross polarised light image of a stained thin section.

Distal silicate alteration

Distinctly hydrothermal alteration is also present in both KLS1-1 and KLS3-1 as represented by plagioclase, pyroxene, garnet, epidote, amphibole and talc. As with dolomitisation, this alteration is preserved as a continuum of textural and mineralogical changes that, while subtle, are identifiable in hand specimen samples. Changes were identified using comparison of rock samples from the same stratigraphic positions in different locations. These changes are described and illustrated in the following section with reference to rock sample photography. The variability of the characteristic compositions and sedimentary textures present within the host rock types (Plate 2-11a & d) are preserved despite hydrothermal alteration. In KLS1-1, the Ekmai Limestone has a very fine-grained glassy texture, coloured white and green, locally containing pods of coarser-grained red garnet, while the overlying Waripi Limestone has the same fine-grained grey dolomite appearance to that observed in KLS3-1. Petrographically this alteration appears as equigranular plagioclase interspersed with coarser grains of pyroxene. Clumps of epidote and garnet were also identified in alteration style. The upper Ekmai Limestone is characterised by isolated quartz grains whereas the middle Ekmai Limestone is devoid of quartz, providing distinction of position within the stratigraphic unit (Figure 2-2). The heterogeneous nature of the Ekmai Limestone is preserved in pyroxene-feldspar and garnet alteration (Plate 2-11a-c). Sandstone has a grainy texture, and although the Ekmai Sandstone is fine-grained it is easily distinguished from limestone or shale. Quartz grains commonly persist in intensely altered zones and grey sand grains are easy to recognise in a matrix of white to pale green pyroxene (Plate 2-11d-f). However, some samples of altered sandstone demonstrate that sand grains have been eroded during calc-silicate alteration (Plate 2-12).

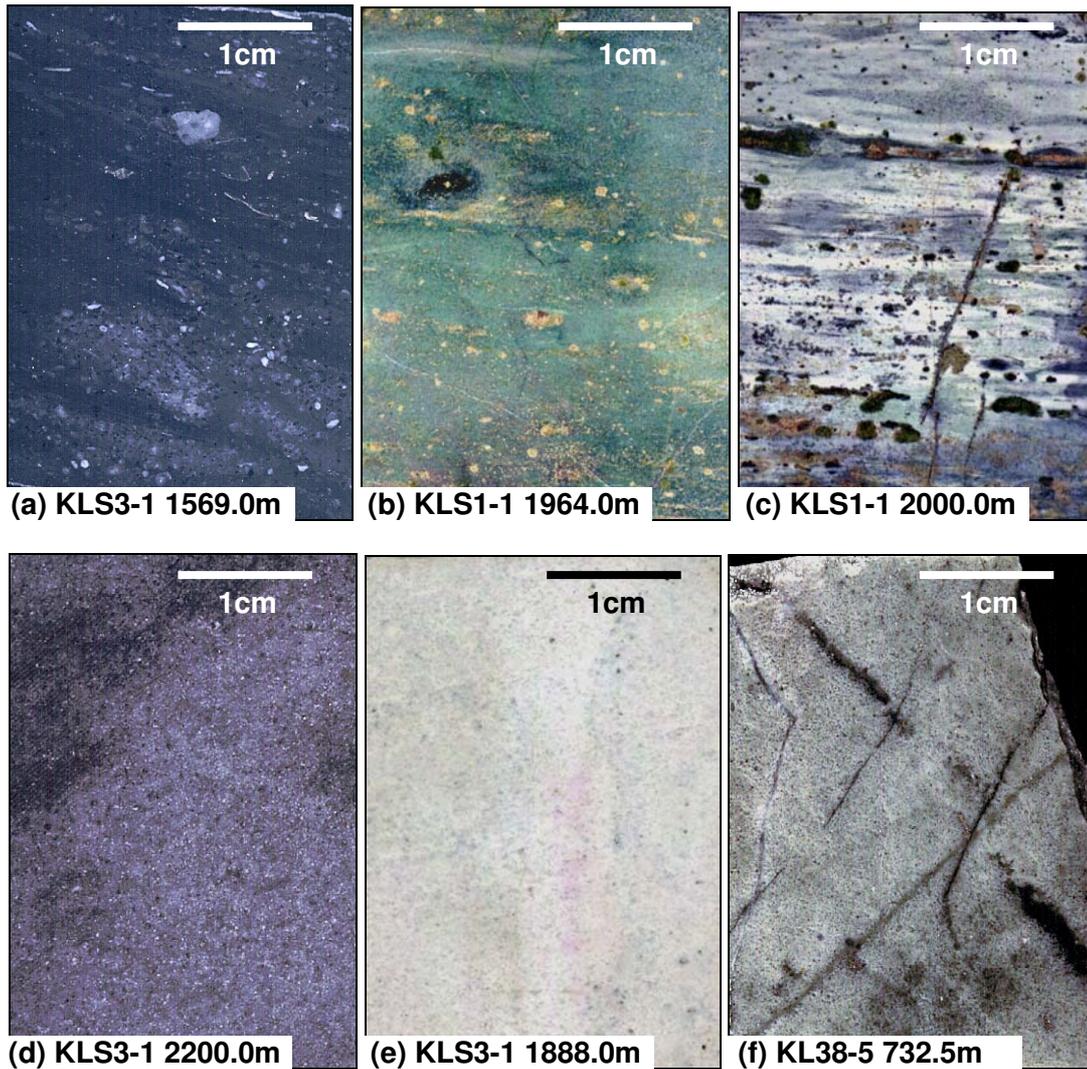


Plate 2-11 Examples of distal hydrothermal alteration

Photographs of samples taken from KLS1-1 and KLS3-1 demonstrating the effects of hydrothermal alteration. (a) Unaltered shale from the upper Ekmai Limestone illustrates the heterogeneous texture created by clusters of organic clasts and sand grains. (b) Green pyroxene and red garnet in altered shale from KLS1-1 displaying excellent preservation of original sedimentary texture as compared to (a). (c) Grey calcite-magnetite/white feldspar/red garnet altered Ekmai Limestone. (d) Unaltered sandstone with the organic material still visible as dark matrix near the top of the photograph. (e) A sample taken from KLS3-1 to illustrate calcite-talc-amphibole alteration of sandstone. (f) An example of clinopyroxene altered sandstone taken from the lowermost part of the mineralised zone in Kucing Liar.

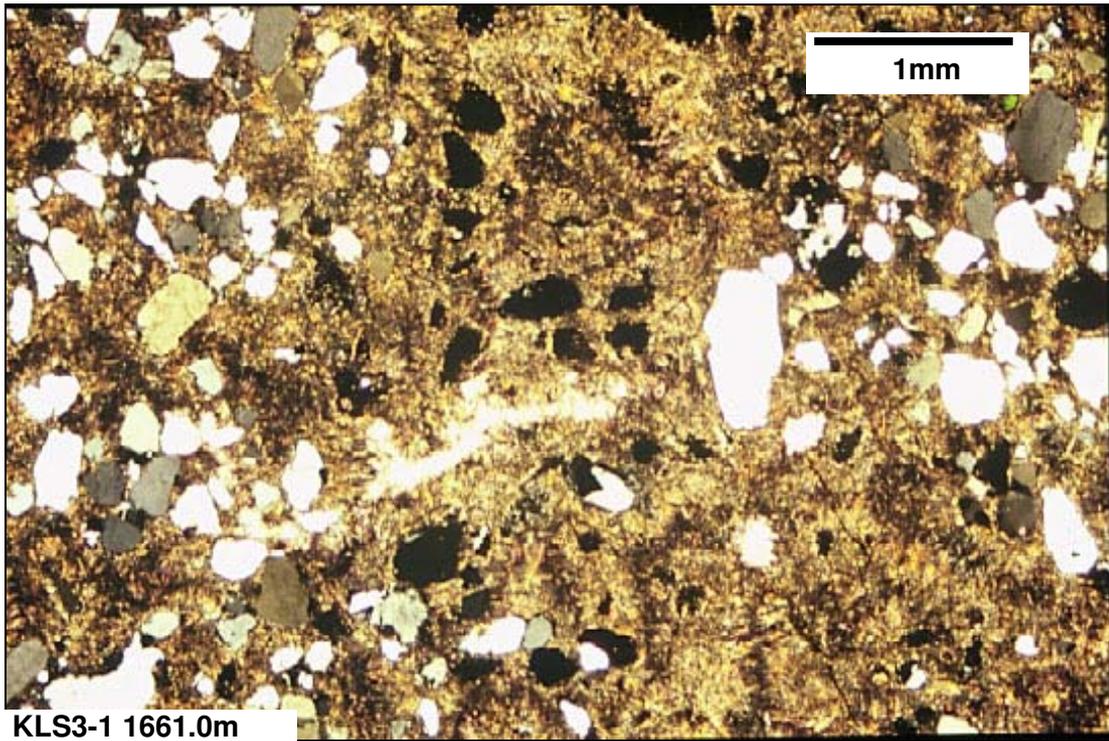


Plate 2-12 An example of hydrothermal micro-textures in sandstone

A photomicrograph of altered sandstone illustrates the progression of hydrothermal alteration. Dissolution of quartz grains (black holes) is associated with replacement of the matrix by amphibole and talc (yellow-brown). Crossed polarised light.

3 Paragenesis

This chapter identifies the paragenetic history of Kucing Liar by documenting the small-scale controls of fluid infiltration, alteration mineralogy and the sequence of mineral development. A large number of minerals are developed during hydrothermal infiltration and some effort is taken to describe and illustrate the various forms and crosscutting relationships in each case. A significant problem at Kucing Liar results from varying wall rock composition and the alteration characteristics are defined here in terms of host rock lithology in order to recognise that influence. The procedures used to define the characteristics of the hydrothermal system are:

1. Identification of minerals generated during hydrothermal activity
2. Determination of paragenetic sequence from crosscutting relationships

A number of drill holes from the main mineralised zone were examined in detail to identify the primary mineralogy and their textures. Samples were collected from split drill core. Thin sections and polished slabs were prepared from each section. Photographs of the split drill core samples are used to illustrate the styles of mineral occurrence and their small-scale structural controls. Initial identification of minerals present in drill core samples was followed by targetted petrography to confirm the identity of many minerals. Mineral compositions are derived from quantitative element oxide analyses collected from a Jeol JXA-600 SEM-EDS microprobe (Appendix III). An XRD method termed GADDS (General Area Detection Diffraction System) was found to be very useful as it is a non-destructive technique that can be applied to mesoscopic (up to 10cm-scale) specimens mounted on a traversable stage and targetted using high magnification video (Figure 3-1, Figure 3-4). Due to the nature of the technique it was possible to analyse individual millimetre-scale alteration bands, which were difficult to distinguish in thin sections.

3.1 MINERAL TEXTURES, ASSEMBLAGES AND TIMING RELATIONSHIPS

Observations of crosscutting relationships were generally confined to examination of split and polished core samples. Minerals occur in a range of textures, including penetrative or selvedge alteration as well as vugh and fracture infill. In the following descriptions, “penetrative alteration” implies no distinct fluid channelway can be observed while selvedge alteration infers the presence of a fluid conduit. “Vein” is used when referring to planar centimetre-scale infill while “fracture infill” refers to millimetre-scale irregular features. The specific temporal relationships between minerals are generally found in crosscutting veins and in particular, their alteration selvedges. Breccia textures were also useful in confirming relationships. The dominant minerals are placed into paragenetic groups based on relative timing. The hydrothermal minerals identified are placed into four groups which reflect similar broad-scale temporal relationships built up by specific timing relationships found in disparate individual samples. Some of these groups are chemically similar while others are not. The minerals within each group generally reflect similar fluid infiltration styles based on the textural setting of mineral development.

Group I paragenesis

This group is a collection of chemically-related calc-silicate and magnesian-silicate parageneses that can be divided into early anhydrous minerals and later hydrous minerals. The inclusion of calcite-magnetite in this group is due to consistent spatial relationships of these minerals to calc-silicate alteration. The parageneses are:

- | | |
|--------------------------------|--|
| a) Calcite ± magnetite | $\text{CaCO}_3, \text{Fe}_3\text{O}_4$ |
| b) Clinopyroxene ± plagioclase | $\text{Ca}(\text{Mg,Fe})\text{Si}_2\text{O}_6, (\text{Ca,Na})(\text{SiAl})_4\text{O}_8$ |
| c) Grossular-andradite | $\text{Ca}_3\text{Al}_2\text{Si}_3\text{O}_{12} - \text{Ca}_3(\text{Fe}^{3+},\text{Ti})_2\text{Si}_3\text{O}_{12}$ |
| d) Humite ± forsterite | $\text{Mg}(\text{OH,F})_2 \cdot 3\text{Mg}_2[\text{SiO}_4], \text{Mg}_2\text{SiO}_4$ |
| e) Chrysotile-serpentine | $\text{Mg}_3\text{Si}_2\text{O}_5(\text{OH})_4$ |
| f) Tremolite-actinolite | $\text{Ca}_2(\text{Mg,Fe})_5\text{Si}_8\text{O}_{22}(\text{OH})_2$ |

Calcite ± magnetite

The earliest hydrothermal mineral association is characterised by calcite plus locally significant amounts of magnetite. Calcite is white, grey, black or orange. It occurs in a variety of forms ranging from penetrative alteration, millimetre and centimetre-scale selvages along simple fractures to complex convoluted bands, while the associated magnetite is developed as discrete spots, commonly but not invariably associated with a recognisable fracture. Where calcite ± magnetite alteration has developed in shale it is uniformly black to dark grey in appearance and very fine-grained with no visible evidence of fluid channelways. Calcite ± magnetite is consistently crosscut by clinopyroxene ± plagioclase (Plate 3-1a, c, e).

Clinopyroxene ± plagioclase

Clinopyroxene ± plagioclase development is typically penetrative and forms relatively sharp contacts with zones of calcite ± magnetite. This alteration produces two very distinct textures depending on whether it is developed in limestone or calcareous shale (Plate 3-1c, f). Plagioclase feldspar (labradorite composition) occurs in subequal quantities with clinopyroxene in calcareous shale but is sporadic in limestone precursors. Rare examples of white plagioclase-only alteration were found (Plate 3-1d). Sedimentary textures of sandstone, limestone/dolostone and shale are generally preserved by clinopyroxene ± plagioclase alteration whose colour and appearance varies consistently with host unit. In limestone and dolostone, the colour of clinopyroxene ± plagioclase varies from white to light green, while it is persistently darker green and much finer-grained where developed in shale (Plate 3-1c). Petrographic studies reveal patterns of clinopyroxene grain size that are coincident with the sedimentary rock texture. It is formed as evenly spaced rosettes of coarser-grains radiating from a fine-grained core in sandstone and as coarse-grained accumulations in a very fine-grained groundmass in peloidal limestone. In shale precursors, clinopyroxene grains are evenly scattered and fine to very fine-grained, and where distinguishable are yellow in contrast to their colourless appearance in limestone.

Rare examples of fluid channelways were recognised during SEM analysis where clinopyroxene is concentrated immediately adjacent to a fracture. These fractures also contained μm -scale infill. Analyses of clinopyroxene conform to a general formula of $\text{Ca}(\text{Mg,Fe})\text{Si}_2\text{O}_6$ ranging from diopside (Hd_{05}) to hedenbergite (Hd_{60}) (Figure 3-2a). The variation of clinopyroxene composition is closely related to lithology. Those in altered limestone/dolostone are restricted to $<\text{Hd}_{20}$, whereas samples from shale have a much larger range in compositions from Hd_{20} - Hd_{60} . Clinopyroxene in porphyry host units has an intermediate composition close to Hd_{20} (Figure 3-2a). Plagioclase developed during Stage I in conjunction with clinopyroxene has two compositional groupings respectively, between An_{20} and An_{40} and closely grouped about An_{60} . Secondary plagioclase developed in porphyry is typically low in albite while in limestone it is more albitic and more varied in composition (Figure 3-2). Plagioclase developed in shale has compositions similar to porphyry and limestone-hosted plagioclase. Plagioclase accompanies clinopyroxene in calcareous shale while clinopyroxene is darker green in hornfelsed shale reflecting higher iron contents (see Chapter 1, Table 1-5).

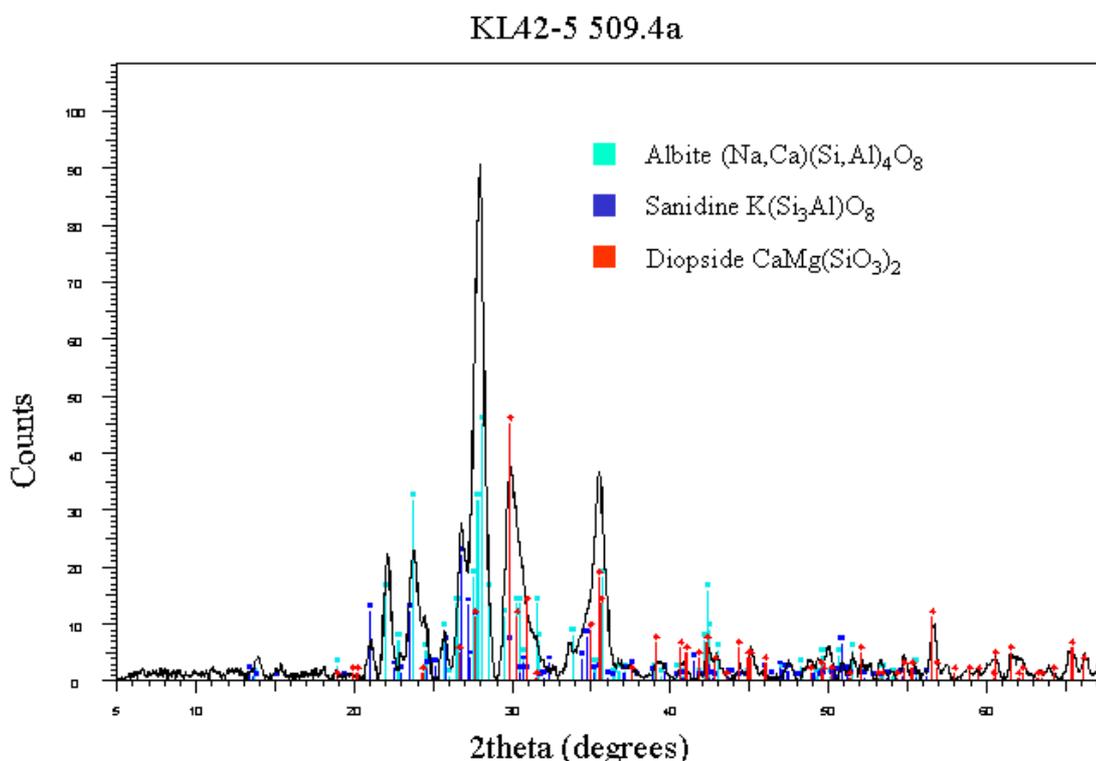


Figure 3-1 Example of GADDS X-ray diffraction identification of hornfels alteration in shale
An overlay of output from an X-ray diffraction analysis from GADDS equipment on library signatures.

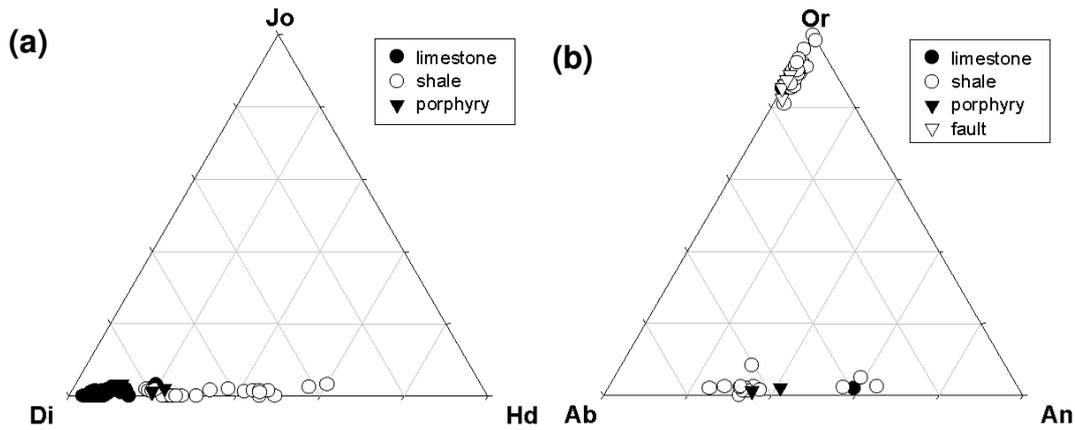


Figure 3-2 Composition of clinopyroxene and feldspar

(a) Clinopyroxene analyses show the chemical control exerted by protolith (b) Plagioclase and orthoclase feldspar compositions identify individual mineral compositions populations but no influence imposed by wall rocks.

Garnet

Garnet varies from green through red, orange and brown intermediate colours in limestone, frequently in the same hand specimen, but is consistently red where developed in shale. Garnet commonly forms 1-10cm scale accumulations that parallel identified sedimentary layering in shale, though widths of 20-50m were observed in drill core (see Chapter 4). In one instance (Plate 3-1e) garnet was observed to occupy the centre of a vein with a pale green clinopyroxene selvage. It is difficult to discriminate between infill and alteration garnet, although examples of recognised infill garnet suggest it forms darker shades of the same colour. The petrographic character of garnet varies in that the green and red varieties are both isotropic, while brown garnets are anisotropic and display concentric growth zones. Garnet timing is problematical and it is possible that the different garnets, coloured from red to green, perhaps developed at different times (Plate 3-1g). Garnet overprints both diopside and hedenbergite \pm plagioclase. There appears to be an early green garnet that was overprinted by brown to red garnet. Green garnet is crosscut by green phlogopite and also by red garnet, while red garnet crosscuts K-feldspar (Plate 3-1h).

Garnet compositions are generally consistent within a single sample (Appendix III) except for sample KL26-8 385.4, which contains two types of garnet (green and red). The primary compositional trend lies along the andradite-grossular series ranging from Ad_{100} to Ad_{40} , the spessartine, pyrope and almandine components within this trend having maxima of Sp_2 , Py_3 and Al_{12} (Figure 3-3). Two analyses from altered shale have relatively high almandine contents. Green garnet from sample KL26-8 385.4m has a composition of approximately $Gr_{80}Al_{12}Py_8$ (Appendix III). Composition is not consistently correlated to lithology (Figure 3-3a) but may be related to small-scale structural setting (Figure 3-3b).

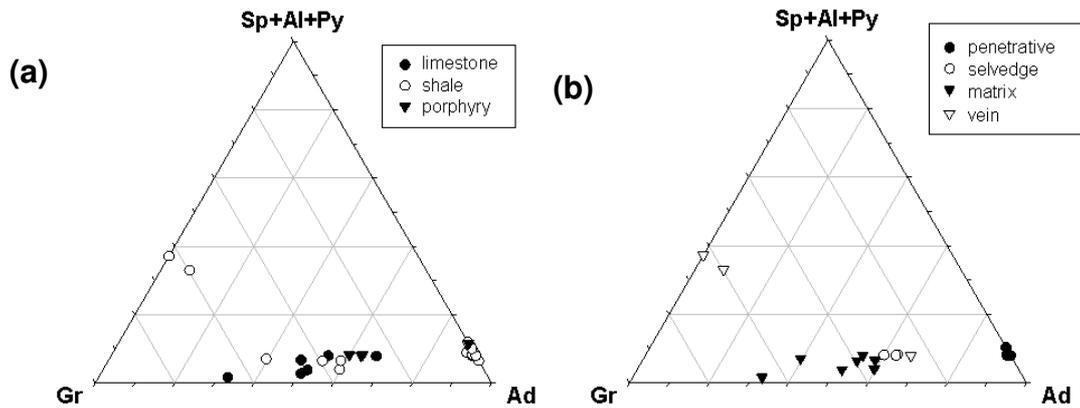


Figure 3-3 Composition of garnet

(a) Garnet analyses divided by protolith (b) Garnet analyses display some correlation with rock texture, penetrative alteration, selvedge alteration, breccia matrix replacement and vein material.

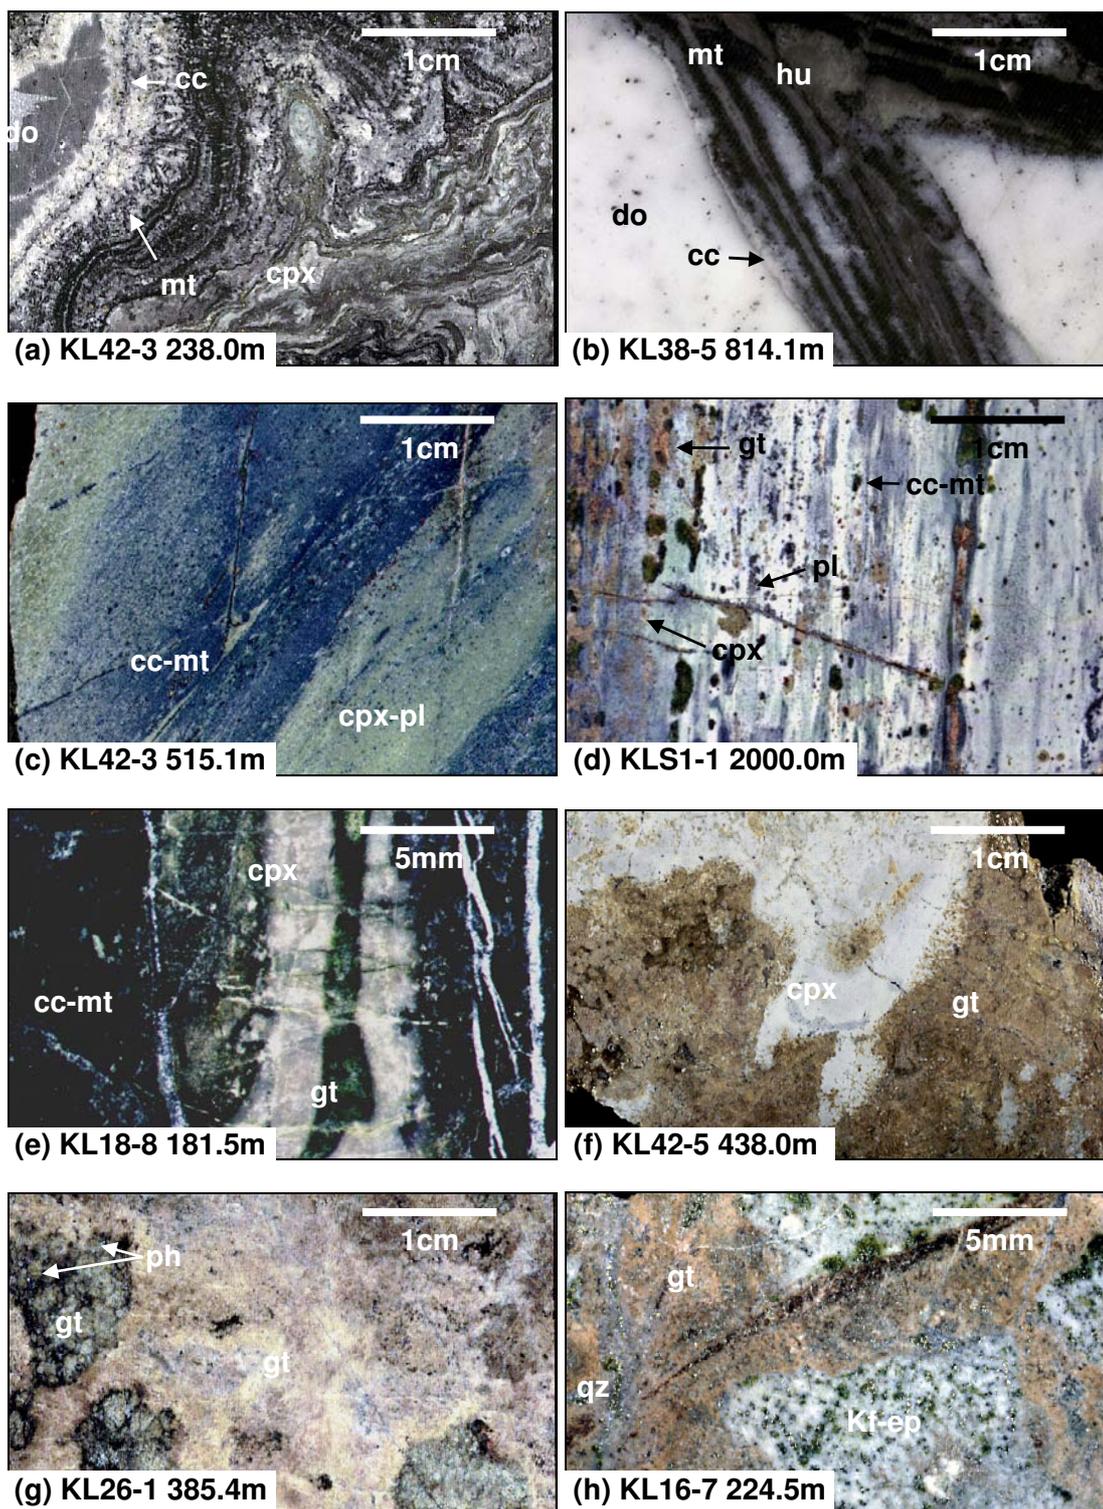


Plate 3-1 Textures and timing relationships of anhydrous Group I minerals

(a) Concentric bands of calcite, magnetite and clinopyroxene (b) Calcite, magnetite and pale brown humite selvages (c) Clinopyroxene-plagioclase band in shale. (d) Hedenbergite-plagioclase-garnet in shale (e) Green garnet vein with white diopside seldge (f) Penetrative white diopside alteration and green-orange coloured garnet. (g) Green garnet with green phlogopite rims in an orange-red garnet matrix. (h) Orange-red garnet selvage alteration crosscutting penetrative white K-feldspar alteration.

Humite ± forsterite ± monticellite

Humite, forsterite and rare monticellite are indistinguishable in hand specimen, though each phase has been identified via petrography and GADDS analysis (Figure 3-4). Humite is the most common; forsterite is subordinate and monticellite rare. These minerals are entirely restricted to dolomitised limestone precursors (Chapter 4). All three minerals are orange-brown (Plate 3-2a, b, c) where fresh but most of the rocks containing them are grey-black due to the presence of retrograde serpentine (Plate 3-2c, e, f). Visible forsterite veins have been identified but are uncommon (Plate 3-2b, f). Petrographic examination shows that euhedral to subhedral, equidimensional grains of humite are either evenly distributed throughout the sample or occur in locally massive concentrations. Grainsize variation of tens of microns occurs around vugs where idiomorphic grains of humite protrude inward. Humite ± forsterite is found to consistently overprint both calcite ± magnetite and clinopyroxene ± plagioclase but has no visible association with garnet. The few examples of crosscutting relationships for humite and forsterite indicate that forsterite developed after humite. Relative timing of garnet and humite-forsterite is not known as these minerals do not coexist. As garnet is closely associated with clinopyroxene, and humite overprints clinopyroxene, it is possible but uncertain that humite-forsterite formed after garnet. Humite alteration is strongly overprinted by serpentine. Though humite is not visible in hand specimens of strongly serpentized rocks, petrographic examination reveals that it is almost always present as isolated grains. Only nine humite samples and one clinohumite sample (7 and 9 Mg atoms respectively) were positively identified by calculation of mineral formula from microprobe compositions (Figure 3-4). Most suspected examples were established as forsterite by calculation of mineral formula from multiple analyses. Significant substitution of Fe for Mg was identified in forsterite and humite, although the amount of iron does not exceed 15wt% Total Fe. In microprobe (Appendix III) analyses of forsterite, iron is higher in vein infill than in selvage and penetrative alteration of wall rock. This broad pattern may be repeated for humite, although the number of analyses is much fewer.

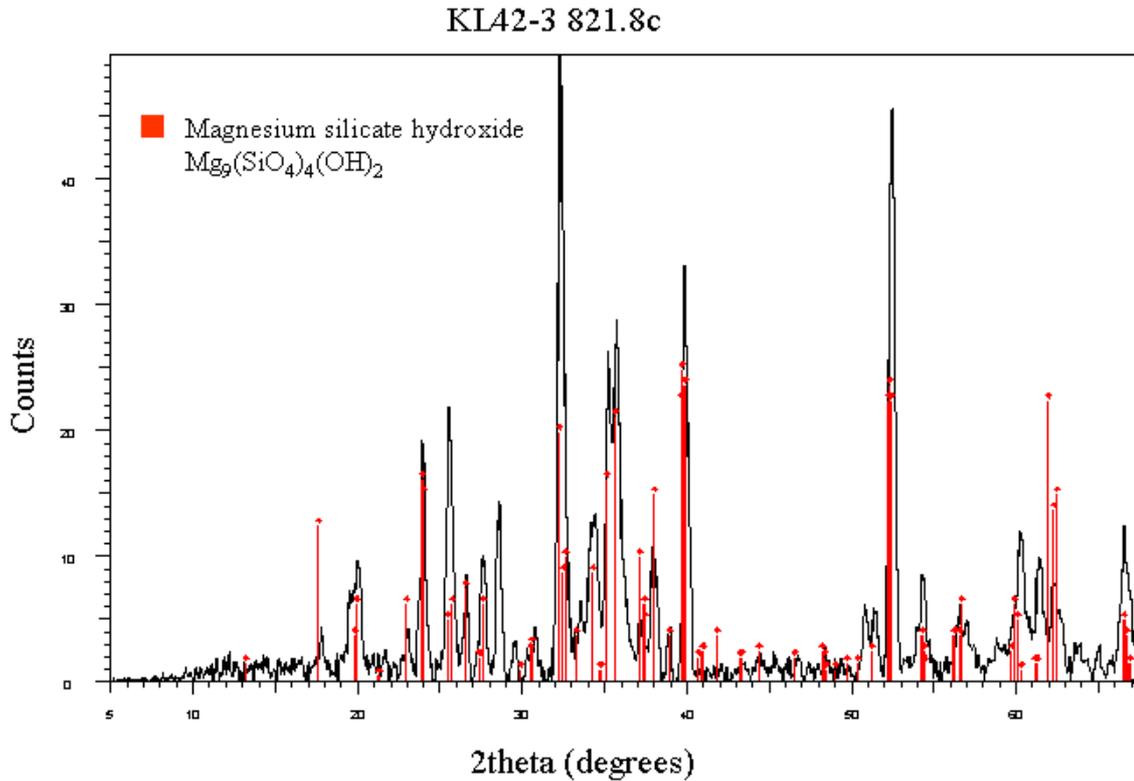


Figure 3-4 Example of GADDS X-ray diffraction identification of a humite group mineral

An overlay of output from an X-ray diffraction analysis from GADDS equipment on a type signature of peaks for a chemically identified library mineral illustrates positive identification of a humite group mineral.

Serpentine

Serpentine is consistently associated with humite ± forsterite (Plate 3-2b, c, e, f) and does not occur in clinopyroxene ± plagioclase ± garnet hornfels. Breccia fragments of humite ± forsterite found in matrices of tremolite-actinolite (next section) commonly have rims of serpentine. Serpentine is dark green to black, very soft and the grainsize varies from microscopic to millimetre-scale. Alteration is very difficult to distinguish from infill though selvage alteration and matrix alteration of fragmented rocks are the most common form at 5mm-1cm scale, rarely extending to 5cm. These fracture selvages commonly form networks in humite ± forsterite altered zones and give the appearance of 10m-scale zones of penetrative chrysotile alteration. Serpentine formed a penetrative overprint of humite ± forsterite alteration zones but is commonly overprinted by strong anhydrite alteration, producing grey-black coloured rocks in which mineral components

are difficult to recognise. Substitution of Fe into serpentine was evident in analyses but was not consistently associated with specific lithology or texture (Appendix III).

Tremolite-actinolite

Tremolite is generally restricted to clinopyroxene-altered precursors and fault zones and varies in colour from dark green, pale green, grey to almost white, although the white variety is probably the product of subsequent alteration by anhydrite and/or talc. Tremolite-actinolite forms 10cm-scale selvages on evenly spaced discrete fractures that are commonly green in penetrative clinopyroxene alteration and grey in humite-serpentine wall rocks (Plate 3-2e, f). Alteration and infill can generally be distinguished in hand sample, as infill is usually coarser-grained, though exceptions occur where grain size is variable due to the wall rock lithology. Tremolite-actinolite commonly overprints clinopyroxene rocks but is also strongly overprinted by biotite, anhydrite and chalcopyrite \pm pyrite. Replacement is gradational and interconnected patches of centimetre-scale tremolite clusters persist away from identifiable channelways. In contrast to the style of tremolite-actinolite development in skarn-altered rocks, tremolite-actinolite alteration hosted in magnetite-bearing wall rocks generally has a different appearance, being paler and forming zones of penetrative alteration up to 10m wide (see Chapter 4). The association with visible fractures is not as clear for tremolite that overprints magnetite as it is for the variety that overprints skarn. Zones of penetrative tremolite-actinolite commonly contain fragments of magnetite that form sharp boundaries with the tremolite and abundant chalcopyrite mineralisation (described below). The tremolite-actinolite grains within these zones are commonly aligned (Plate 3-2h), implying a shearing component. Microprobe analyses examples are split evenly between tremolite and actinolite (Appendix III) independent of the form of mineral development. There is some preference for infill and matrix growth to be tremolite and for selvage replacement to have actinolite. Analyses from shear-hosted samples have the lowest variability. Compositions are consistent within each sample.

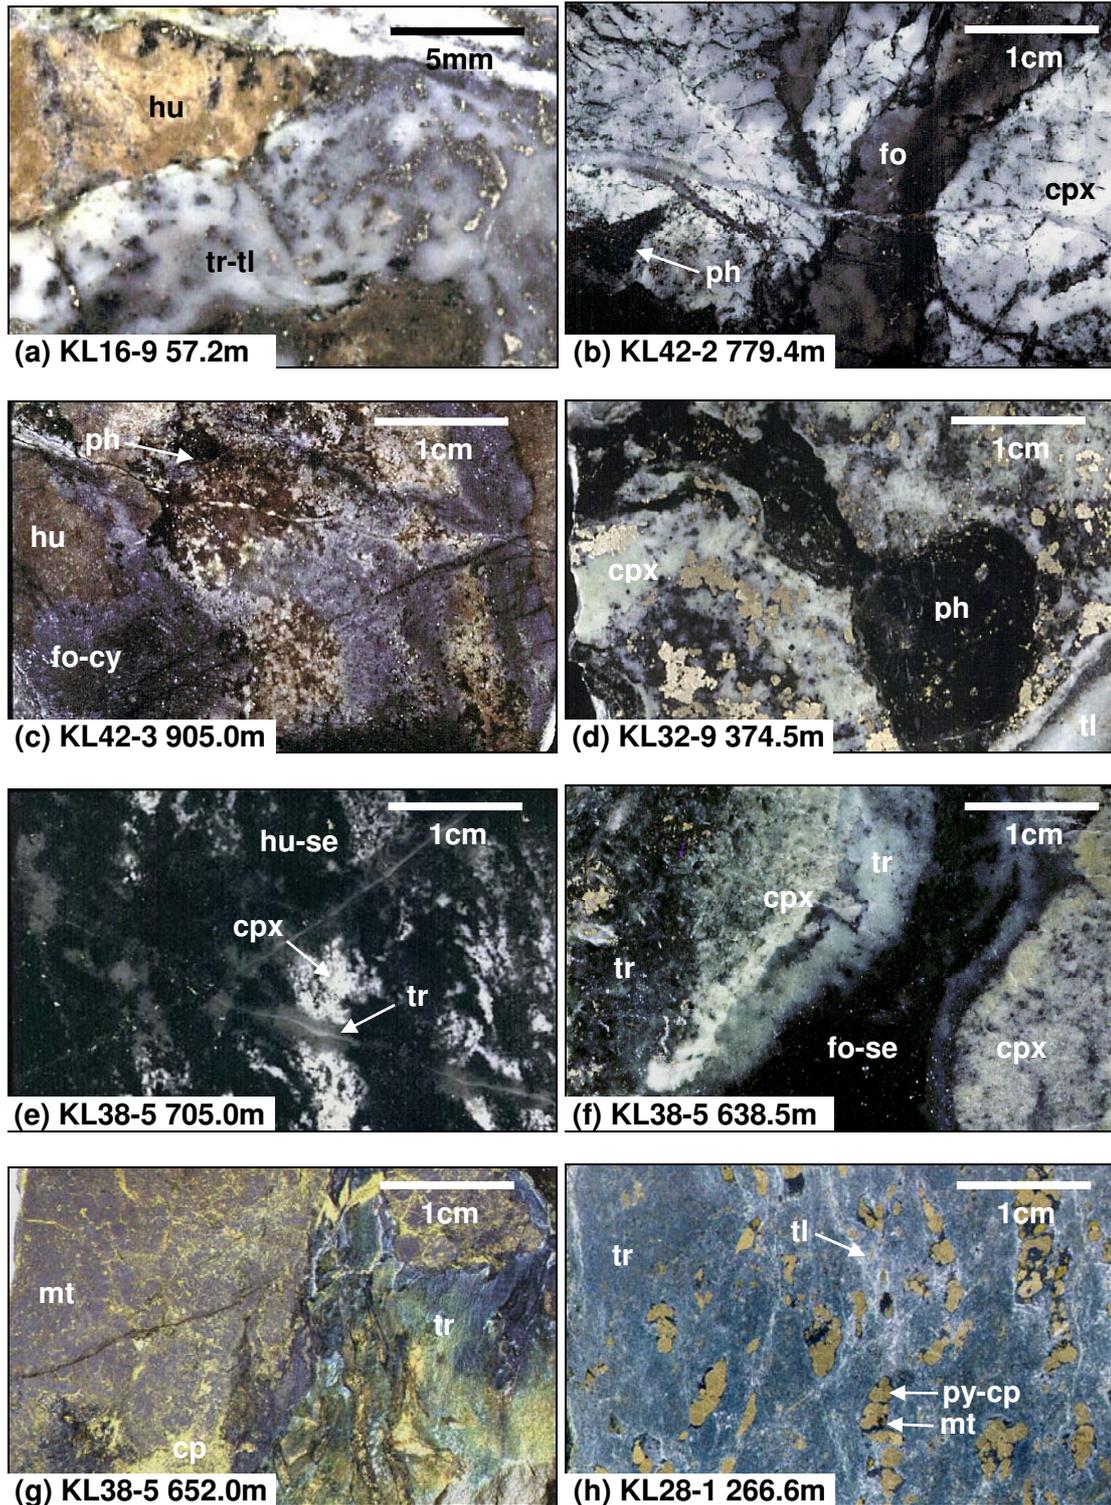


Plate 3-2 Textures and timing relationships of hydrous Group I minerals

(a) Humite fragment tremolite, talc and anhydrite matrix. (b) Forsterite vein crosscutting white diopside and overprinted by tremolite-actinolite and talc. (c) Orange-brown humite fragments in forsterite-chrysotile matrix. (d) Phlogopite alteration in clinopyroxene. (e) Clinopyroxene and humite overprinted by serpentine and tremolite (f) Serpentine and tremolite overprinting of forsterite vein in clinopyroxene wall rock. (g) Tremolite-actinolite around magnetite fragment. (h) Fibrous tremolite containing fragments of magnetite altered to pyrite-chalcopyrite.

Group II

This group is defined by potassium minerals, but also includes quartz veins which are consistently associated with K-feldspar alteration and magnetite as it appears to have a consistent temporal relationship. The minerals included in this group are:

- | | |
|-----------------|---|
| a) K-feldspar | KAlSi_3O_8 |
| b) Quartz veins | SiO_2 |
| c) Mica | $\text{K}(\text{Mg,Fe})_3[\text{Si}_3\text{AlO}_{10}](\text{OH})_2$ |
| d) Magnetite | Fe_3O_4 |

K-feldspar

K-feldspar occurs primarily as penetrative alteration of clinopyroxene \pm plagioclase hornfels (Plate 3-3b, f, h), though examples of low intensity K-feldspar indicate association with fractures which contain sub millimetre-scale infill (Plate 3-3). Although its development is largely restricted to calcareous shale, K-feldspar is also, albeit rarely, present in rare centimetre-scale veins and selvage alteration in altered limestone (Plate 3-3f). K-feldspar is very commonly accompanied by subordinate brown biotite producing a pale brown coloured rock (Plate 3-3d, e). The relative timing of K-feldspar is well constrained as it overprints clinopyroxene-plagioclase alteration and is consistently overprinted by biotite (Plate 3-3). Where K-feldspar has been identified in limestone it is consistently found to overprint green phlogopite (Plate 3-3f). Analyses of K-feldspar from veins, selvage alteration and penetrative alteration in both shale and from an unknown precursor lithology have consistent compositions from $\text{Or}_{90}\text{-Or}_{100}$ and are indistinguishable from each other (Figure 3-2; Appendix III).

Phlogopite-biotite

Mica occurs as both green and brown varieties, which have consistent crosscutting relationships. The green variety is referred to here as phlogopite while the brown is referred to as biotite. Phlogopite and biotite most commonly forms locally penetrative centimetre to metre-scale coarse-grained accumulations. They are locally abundant associated with millimetre to metre scale fracturing and fragmentation and it is difficult to distinguish infill and alteration as euhedral crystals are common although alteration appears to be their more dominant form. Petrographically, phlogopite is pale to transparent, with weak to moderate pleochroism the same as the visible colour, while biotite is much darker brown in colour, though pleochroism is still strong. Phlogopite is generally found in limestone and biotite in shale, however there are some exceptions, brown varieties of phlogopite found associated with humite and more rarely with clinopyroxene. The relative timing of green phlogopite is well constrained by consistent relationships where it crosscuts clinopyroxene, green garnet and humite-forsterite and is overprinted by K-feldspar. Biotite is regularly developed with K-feldspar as very pale brown fracture selvage alteration around fracture networks in massive K-feldspar (Plate 3-3). Biotite occurs more frequently in hornfels-altered rocks but is not totally restricted to this lithology (Plate 3-3). Biotite alteration is generally fine to very fine-grained. Infill associated with K-feldspar microfractures is generally sub-millimetre scale while in quartz it is millimetre-scale.

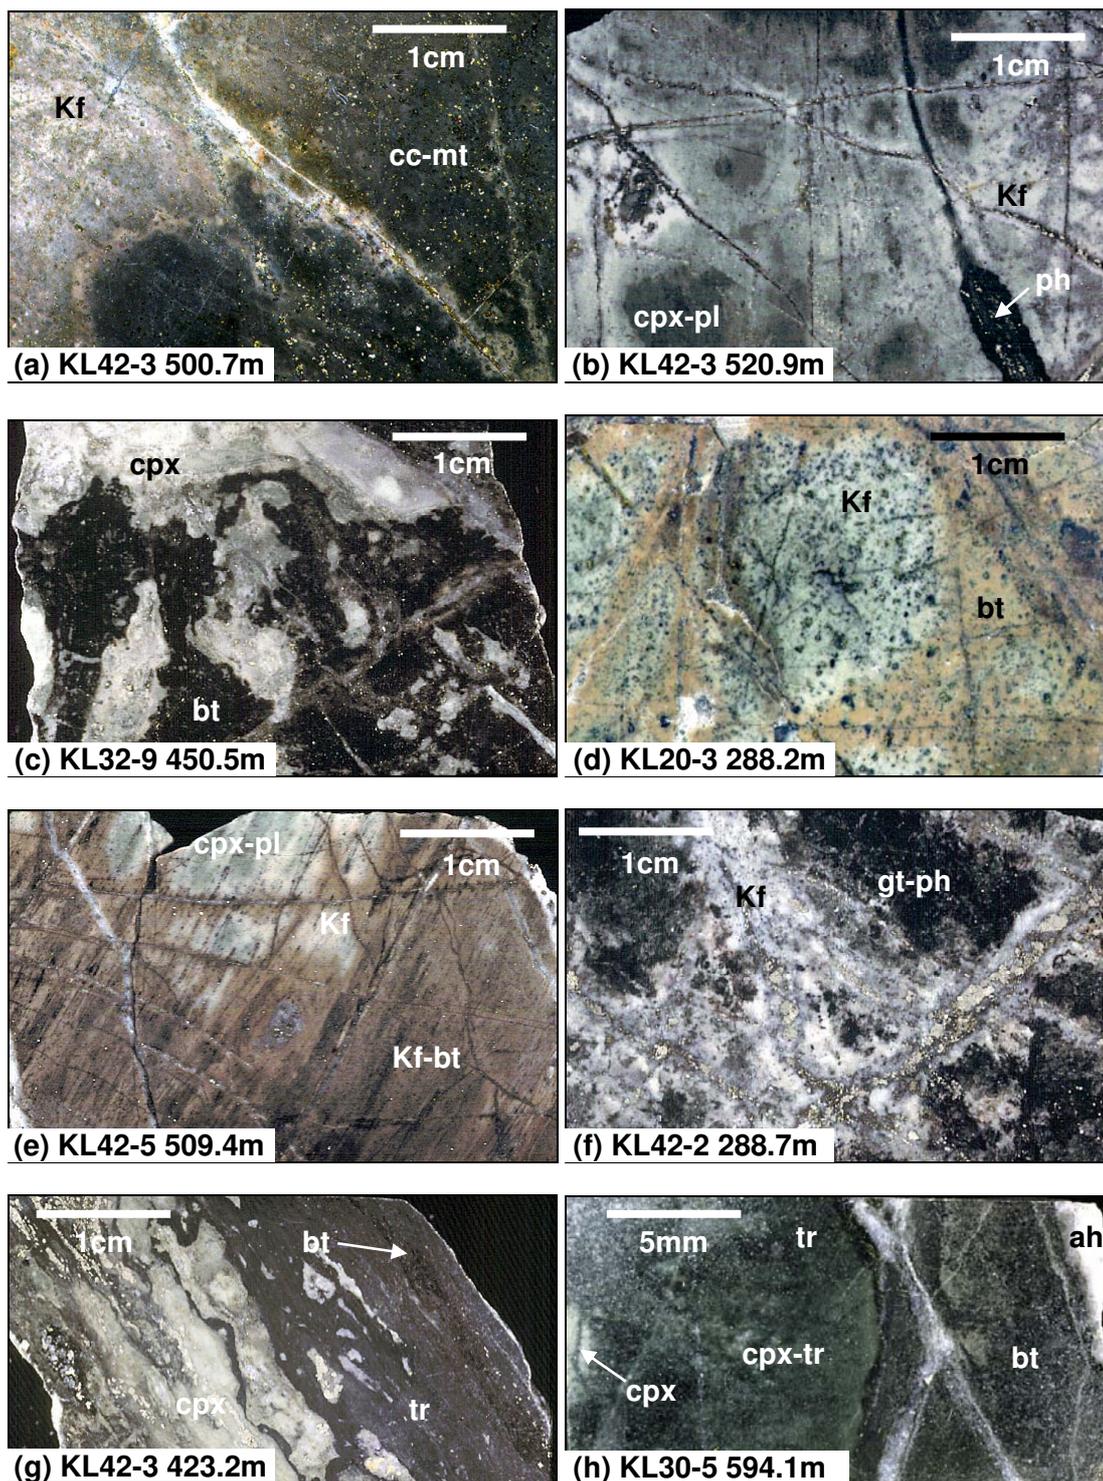


Plate 3-3 Textures and relative timing of potassic Group II minerals

(a) *K-feldspar overprint of calcite-magnetite hornfels* (b) *Dark green clinopyroxene-plagioclase hornfels crosscut by white K-feldspar selvages* (c) *Biotite selvages in penetrative clinopyroxene* (d) *Pale biotite selvages in white K-feldspar hornfels.* (e) *Progressive clinopyroxene-plagioclase, K-feldspar + biotite alteration of shale.* (f) *Fragments of garnet and green phlogopite surrounded by selvages of K-feldspar in a limestone precursor.* (g) & (h) *Two examples of tremolite-actinolite crosscut by biotite along the same fracture system in limestone.*

Quartz veins

A set of quartz veins that are consistent in size and spacing is associated with potassic alteration due to temporal relationships. These veins are most commonly 1cm-scale but range from 5mm-10cm and are composed of 2-5mm equant, subhedral to euhedral crystals. There is no alteration selvage around quartz infill. Vein patterns vary from evenly spaced, sheeted arrays to multidirectional stockworks. Quartz veins are most abundant in shale and porphyry but also occur in clinopyroxene-altered limestone (Plate 3-4). Quartz veins crosscut K-feldspar altered rocks and do not contain any K-feldspar infill. An ambiguous relationship with coarse-grained biotite exists where quartz infill occurred after biotite in fractures which contrasts with biotite infill within a quartz vein (see geochronology section below). SEM investigations found microscopic titanite infill within a quartz vein sample.

Magnetite

Magnetite occurs in a variety of textural forms but most commonly as fine to medium-grained penetrative alteration. Ghost fragmental textures can be seen in samples that have been completely altered to magnetite that imply earlier rock fragmentation (Plate 3-4). Breccias with preserved precursor fragment mineralogy are found at the margins of zones of penetrative magnetite alteration (Plate 3-4). Grainsize variations can often be used to identify coarser-grained infill, but are not reliable. Other textural styles include semi-penetrative alteration in shale, isolated grains and fracture infill without associated alteration. Magnetite fracture infill is commonly irregular although regular fracture patterns were identified. Magnetite is largely confined to limestone precursors although some significant accumulations occur in fault zones and at stratigraphic contacts (see Chapter 3). While fracture-related magnetite crosscuts quartz veins and K-feldspar alteration (see Group III section), penetrative styles of magnetite are only consistently found to crosscut calc-silicate alteration. Analyses of magnetite indicate some substitution of magnesium into the lattice, up to 10 wt% MgO, but no consistent pattern to the variation could be identified (see Appendix III).

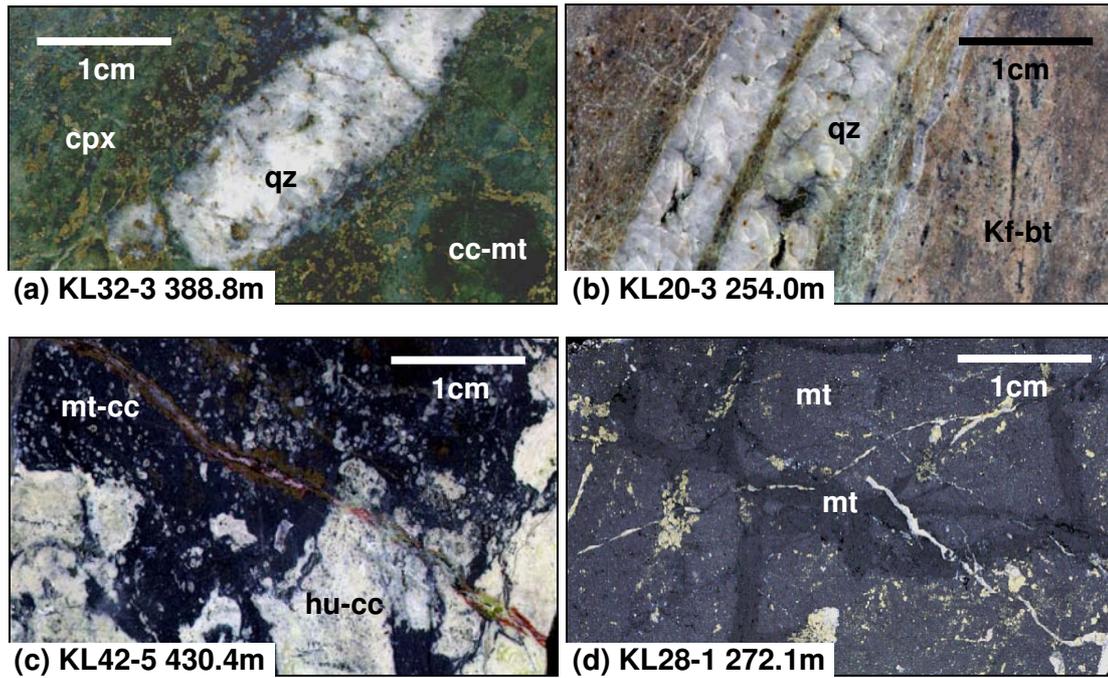


Plate 3-4 Textures and relative timing of non-potassic Group II minerals

(a) Quartz veins in penetrative clinopyroxene alteration (b) Quartz veins in K-feldspar-phlogopite hornfels.
 (c) Magnetite matrix surrounding calcite-altered humite fragments (d) Penetrative magnetite alteration of fragments surrounded by darker magnetite matrix.

Group III

This group is dominated by quartz (silicification) but also includes muscovite, talc and anhydrite. The distributions of minerals in this group are primarily influenced by host rock chemistry. Anhydrite is included as appears to be temporally-related. Some GADDS-XRD analyses suggested the presence of diaspore but it has not been petrographically confirmed. The minerals included in this group are:

- | | |
|--------------|--|
| a) Anhydrite | CaSO_4 |
| b) Quartz | SiO_2 |
| c) Muscovite | $\text{KA}_2[\text{Si}_3\text{AlO}_{10}](\text{OH})_2$ |
| d) Talc | $\text{Mg}_3[\text{Si}_4\text{O}_{10}](\text{OH})_2$ |

Silicification

Silicification is most commonly grey but varies from black to white. The colour variation is linked to grain size such that white quartz is fine-medium grained while darker quartz is very fine-

grained. Black quartz is grey to white when crushed and viewed by binocular microscopy. This colour variation is reflected by infill and alteration textures (Plate 3-5c, d). Silicification generally forms 10-20cm scale selvages about individual fractures, the colour changing from white to black with distance from the fracture (Plate 3-5d). Quartz alteration occurs in all wall rocks and all previously formed alteration. Zones of penetrative quartz alteration are commonly associated with millimetre to centimetre scale, regular to irregular vughs, which occur in both clinopyroxene and K-feldspar altered rocks. The timing of quartz alteration is constrained by rare examples of quartz selvage alteration that overprint magnetite and tremolite-actinolite. The exclusion of magnetite, chrysotile and tremolite-actinolite from zones of quartz alteration where the two are juxtaposed is also used as evidence to constrain the abundant replacement quartz. Mutually exclusive muscovite and talc cannot be directly compared for timing purposes. However, the consistent associations of both of these minerals with quartz alteration, plus their similar relative timing to other minerals (talc is established as post-tremolite, while muscovite is established as post-biotite) are used as evidence that they both belong to Group III.

Anhydrite

Anhydrite is almost ubiquitous in low concentrations in rock samples from Kucing Liar but does not occur in quartz alteration. It is white to pale pink/purple in colour. It forms centimetre-scale vein and vugh infill (Plate 3-5b) devoid of associated alteration, as well as centimetre-scale fracture selvage and metre-scale penetrative alteration. Some samples suggest that anhydrite may preferentially replace Group II quartz veins (Plate 3-5a). Veins of anhydrite in clinopyroxene-plagioclase hornfels appear spatially associated with, and similar in style to, Group II quartz veins. Anhydrite invariably crosscuts tremolite where the two are found together, and occupies the centres of tremolite channelways. Relationships between anhydrite, quartz-muscovite and chalcopyrite mineralisation (Plate 3-5g, h) indicate that anhydrite post-dates quartz \pm muscovite alteration and predates Stage IV pyrite alteration and copper mineralisation. Overprinting of anhydrite by locally penetrative pyrite also supports timing relationships for anhydrite and chalcopyrite.

Muscovite – talc

These two minerals do not occur together and are believed to represent the same process in different host rocks. Talc is commonly associated with quartz alteration of clinopyroxene rock, while muscovite accompanies quartz alteration of K-feldspar rocks (Plate 3-5a, b). Both minerals are fine-grained and frequently form penetrative replacement and, rarely, veins and wispy fracture networks (Plate 3-5g, h). Muscovite and talc occur as haloes around vughs and fractures and as botryoidal infill in vughs (Plate 3-5e, f). Muscovite crystals are generally less than 50µm (see Chapter 6).

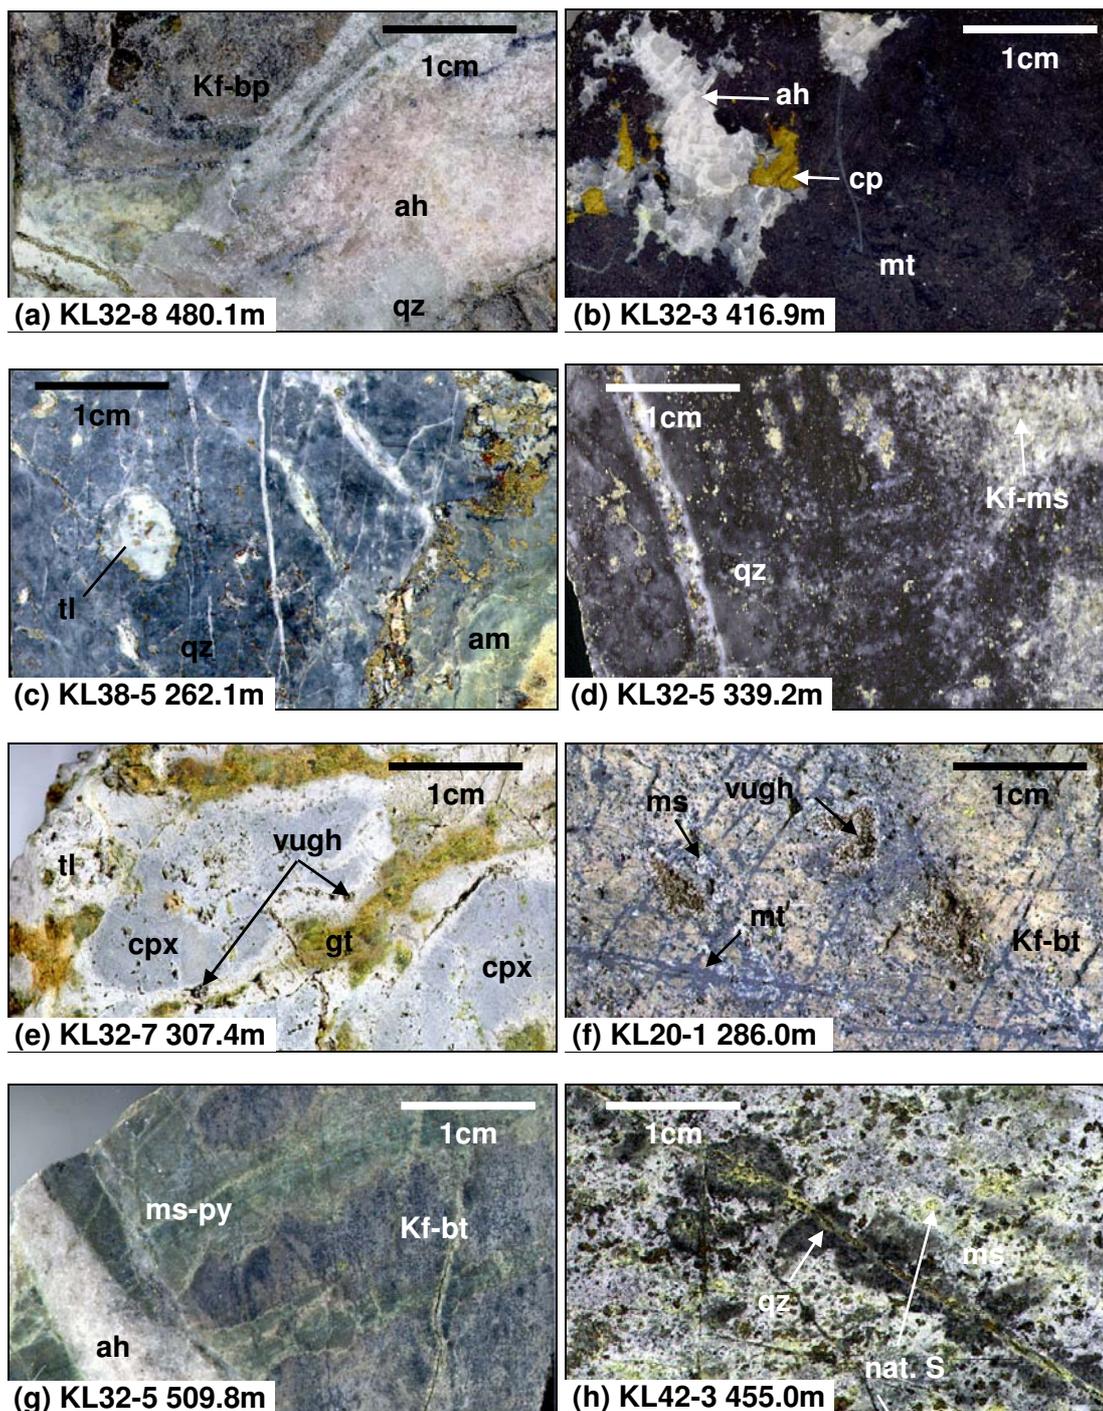


Plate 3-5 Textures and timing relationships of Group III minerals

(a) Anhydrite alteration of quartz vein (b) Anhydrite infill with chalcopyrite in magnetite. (c) Fine-grained grey quartz of clinopyroxene-tremolite altered limestone, a fragment of which is now talc. (d) Quartz + muscovite alteration of K-feldspar altered shale centred on a millimetre scale vein (left). The quartz alteration is peppered with fine pyrite and covellite spots. (e) Leach holes in clinopyroxene-garnet altered limestone associated with talc development. (f) A tension array of magnetite infill truncated by leach holes in K-feldspar-biotite altered shale lined with muscovite. (g) Anhydrite vein crosscutting muscovite-pyrite selvage alteration in a K-feldspar-biotite altered rock. (h) Patches of muscovite + native S alteration associated with quartz selvage alteration in shale.

Group IV

Sulphide minerals dominate this group although minor amounts of fluorite, calcite, anhydrite and serpentine are included. This group includes copper mineralisation as well as locally significant accumulations of molybdenite and galena-sphalerite. The various assemblages recognised in the group are:

a) Pyrite	FeS_2
b) Pyrrhotite	Fe_{1-x}S
c) Chalcopyrite \pm bornite \pm digenite	FeCuS_2 , Cu_5FeS_4 , Cu_9S_5
d) Covellite \pm enargite (\pm pyrite)	CuS , Cu_3AsS_4 , FeS_2
e) Nukundamite \pm covellite \pm chalcocite	$\text{Cu}_{5.5}\text{FeS}_{6.5}$, CuS , Cu_2S
f) Molybdenite	MoS_2
g) Sphalerite – galena	ZnS , PbS
h) Native sulphur	S

Pyrite-pyrrhotite

There are two forms of pyrite in the Kucing Liar system. The first is very fine-grained (sub-millimetre scale) and is a muddy brass colour, while the second is consistently coarser grained (millimetre-scale) and is a brassier yellow colour (Plate 3-6). The first type is referred to as fine pyrite and the second as coarse pyrite and the two commonly occur together. Both types occur as low abundance accumulations in the form of discrete spots and as higher intensity selvages along fractures (Plate 3-6). Fractures typically contain slightly coarser grained infill. Selvages of pyrite alteration extend for tens of centimetres from fractures. Pyrite alteration is commonly penetrative and commonly constitutes 80-100% of the rock. Locally penetrative pyrite including thick accumulations of fine and coarse-grained pyrite crosscut penetrative quartz alteration. It occurs in all rock types but is most common associated with magnetite and quartz alteration (Plate 3-6). It can be difficult to distinguish coarse pyrite infill from alteration, as crystalline pyrite is a common alteration product. Lenses of massive fine and coarse pyrite crosscut penetrative magnetite and quartz alteration providing the primary criterion for its timing. Massive pyrite also crosscuts

anhydrite vein material, establishing the timing of these two minerals. Coarse pyrite appears to overprint fine pyrite, suggesting some continuous progression between the two species. Pyrrhotite occurs in similar settings to chalcopyrite and pyrite (Plate 3-6), though it is rare. Metre-scale zones of 50-100% pyrrhotite are the most common while low abundance accumulations of pyrrhotite are rare. Pyrrhotite is almost wholly restricted to major unit contacts and fault zones where it is invariably associated with locally abundant pyrite and/or chalcopyrite hosted by more extensive zones of intense magnetite alteration (Chapter 2). The relative timing of pyrite, pyrrhotite and chalcopyrite is commonly ambiguous, but where it is clear, there is a consistent sequence of pyrite → pyrrhotite → chalcopyrite (Plate 3-6c).

Chalcopyrite ± bornite ± digenite (± anhydrite)

Chalcopyrite is the dominant copper bearing sulphide in Kucing Liar and can be found in all alteration types except muscovite and talc. It has two distinct styles of development; most commonly as low intensity spots and fractures as well as 0.1-1m scale zones of locally penetrative alteration. It typically occurs as low abundances (<2%) although locally massive 1m-scale concentrations with 80-100% chalcopyrite are present (Chapter 4). There are changes of chalcopyrite form in some samples from spots to fracture infill that may represent the change from alteration to infill. Chalcopyrite commonly occurs with pyrite, though discrete occurrences of either sulphide are also common (Plate 3-6). Petrographic examination indicates that rare purple bornite and rarer blue-grey digenite both occur at the rims of chalcopyrite grains (Plate 3-6), and that digenite is consistently associated with bornite. The presence of chalcopyrite adjacent to, but not within vughs (Plate 3-5), suggests that leaching, which is directly associated with covellite mineralisation (see below), occurred after some form of chalcopyrite mineralisation. However, chalcopyrite is seen to overprint quartz alteration along with pyrite, indicating that while it predates muscovite, it postdates quartz alteration.

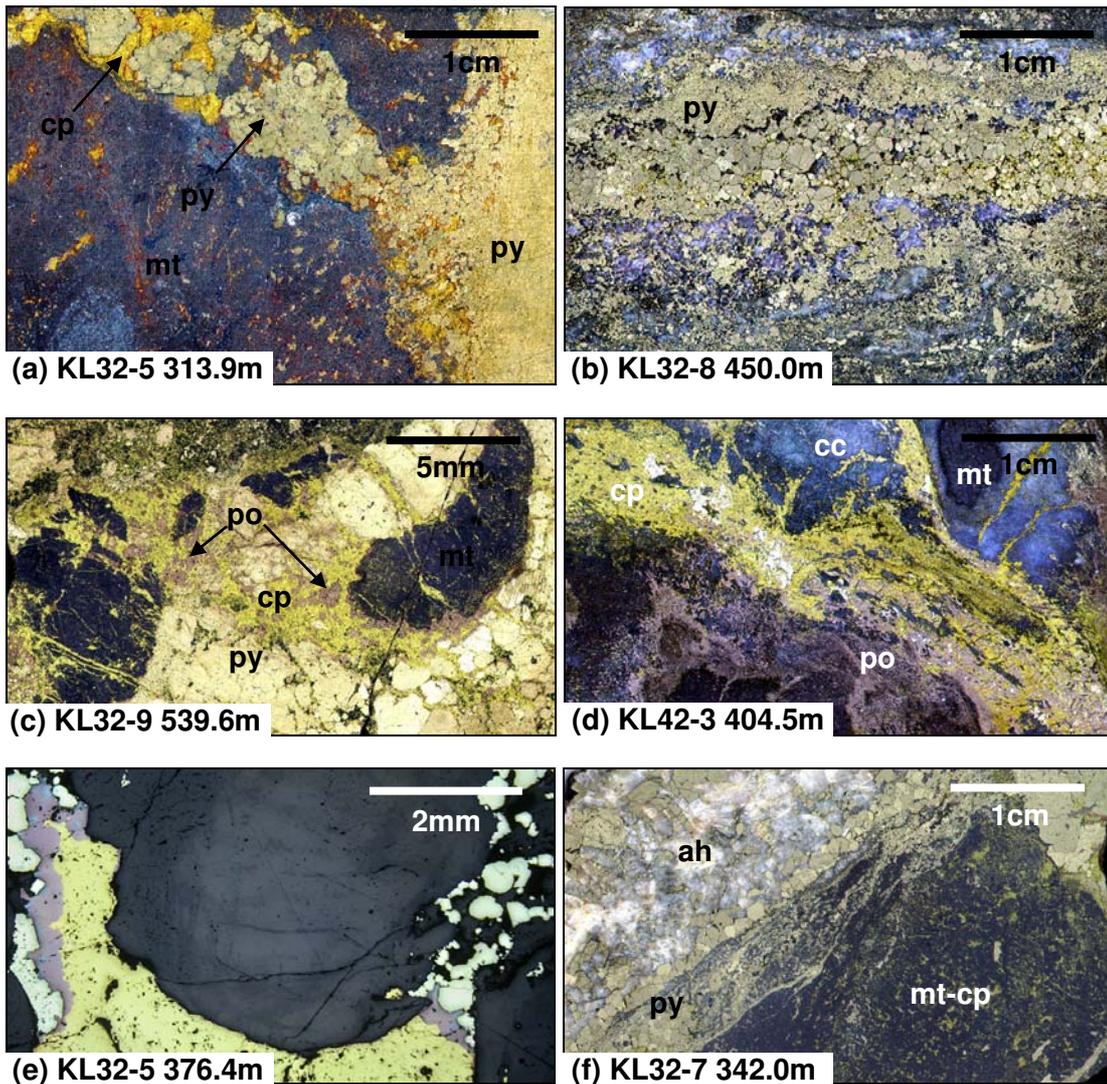


Plate 3-6 Textures and timing relationships of pyrite, pyrrhotite and chalcopyrite

(a) Pyrite alteration band including chalcopyrite in penetratively magnetite altered wall rock. Some oxidation of the sulphide minerals allows clear distinction (b) Brassy coarse pyrite selvage alteration in penetrative quartz alteration taken from the middle of a 20m zone of +80% pyrite. Darker yellow chalcopyrite is visible along the middle of the pyrite. (c) Fragments of pyrrhotite in a chalcopyrite-only matrix which crosscuts pyrite and magnetite fragments. (d) Selvage alteration and fracture infill of pyrrhotite-only and chalcopyrite-only enhance the outline the penetrative alteration of magnetite by calcite. Stringers of chalcopyrite crosscut the pyrrhotite. (e) Purple bornite and minor blue digenite alteration products at the edge of an area of chalcopyrite infill in a quartz vein. (f) Pyrite-chalcopyrite mineralisation crosscutting an anhydrite vein that is hosted by penetrative magnetite alteration. The locally penetrative pyrite is considered to form later than the chalcopyrite which is abundant in magnetite but absent in the anhydrite vein.

Covellite ± enargite ± pyrite ± native sulphur (± fluorite)

Covellite is largely restricted to specific alteration assemblages; namely, silicified and muscovite-altered rock types, although one occurrence was found in a diopside-altered rock. Fluorite is rare but occurs in association with covellite and pyrite (see Chapter 4). Covellite occurs in fractures (Plate 3-7) and vughs as infill and forms metre-scales accumulations of 40-50% by volume. Covellite grain size is commonly sub-millimetre but millimetre-sized hexagonal crystals are not uncommon, especially within vughs. Visibly identified enargite was confirmed petrographically and is consistently associated with covellite (Plate 3-7). It is black to steel grey in hand specimen but has a pale pinkish colour when viewed in reflected light. Native sulphur occurs as infill of holes either alone or associated with pyrite-covellite. Bright yellow native sulphur is also present in distal alteration associated with quartz-dolomite-anhydrite infill of dissolved fossils (Chapter 2). Rare examples indicate that covellite ± fine pyrite overprints chalcopyrite ± brassy pyrite (Plate 3-7). However, in general, the two do not coexist.

Nukundamite, chalcocite

Nukundamite occurs as individual millimetre-scale grains and has been found in calcite (Plate 3-7) and muscovite. This assemblage is associated with muscovite alteration as well as calcite infill around pyrite breccia fragments. It is salmon pink in hand specimen and orange, exhibiting strong bireflectance when observed microscopically in reflected light. Chalcopyrite and covellite occur as laths within grains of nukundamite, while chalcocite occurs as rims at the outer edge of grains. Chalcocite was found associated with both nukundamite and covellite. Chalcocite is soft with a bluish-grey colour in hand specimen and is silver-grey microscopically.

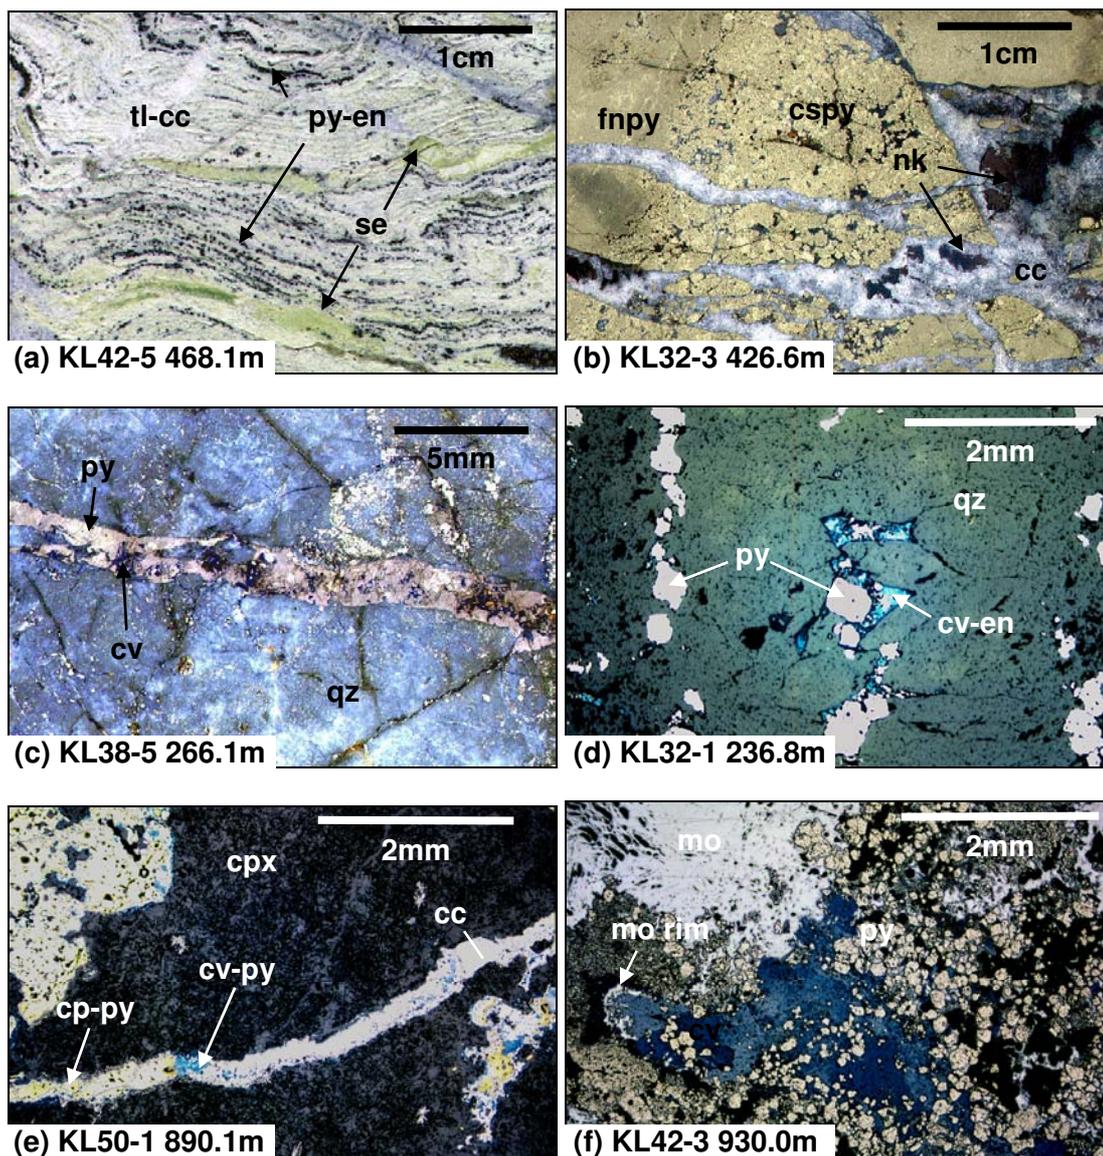


Plate 3-7 Textures and relative timing of covellite, enargite and nukundamite

(a) Bands of talc-calcite and serpentine plus thin black bands of pyrite \pm enargite. (b) Fragments of fine and coarse pyrite in a calcite matrix that contains later nukundamite infill. (c) A thin vein of pyrite-covellite crosscutting penetrative quartz alteration. The sample has been finely polished to enable visibility of the blue covellite, which makes the pyrite appear a pinkish colour. (d) Covellite-enargite infill after pyrite in a quartz vein after crystalline pyrite. (e) Covellite-pyrite replacement along segments of millimetre-scale chalcopyrite-pyrite veinlets and as rims around clusters of chalcopyrite-pyrite. (f) A rim of molybdenite formed on covellite. The relationship of the molybdenite rim with the remaining solid patches of molybdenite in the view is uncertain.

Sphalerite ± galena

In addition to copper mineralisation, there are minor occurrences of lead and zinc in the form of galena and sphalerite. Sphalerite is black to brown in colour with poor crystal development. Sphalerite and galena frequently occur together as locally dense accumulations at the upper margins of the mineralised zone (Chapters 4 & 5), hosted in calcite or clinopyroxene ± garnet alteration (Plate 3-8a). Accumulations of galena-sphalerite are commonly 10cm scale, extending rarely to metre scale. They are most usually in the form of fracture infill or as replacement of matrix in fragmented rocks and polymictic breccia.

Molybdenite

Molybdenite forms radiating crystal masses and is restricted to the lowermost sections of the mineralised zone (Plate 3-8b). It is present as fracture infill and mm-scale selvage alteration most commonly hosted in quartz veins and anhydrite veins or anhydrite alteration.

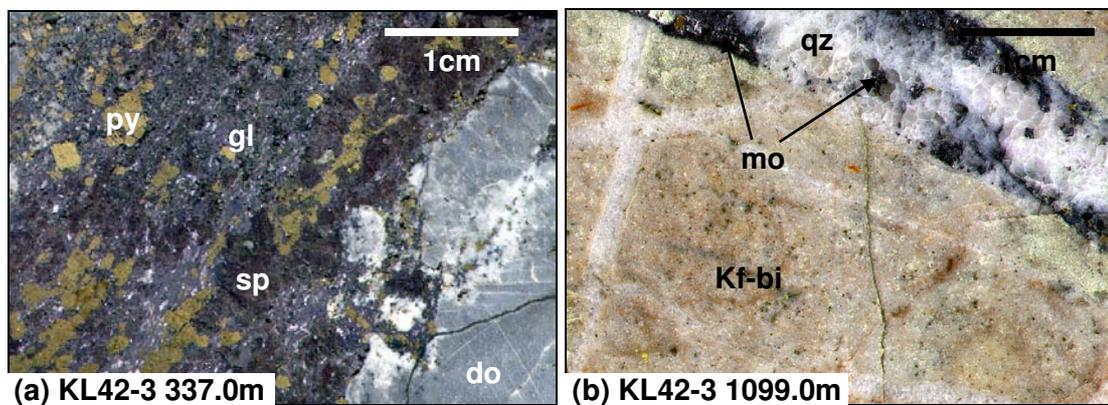


Plate 3-8 Textures and timing relationships of galena, sphalerite and molybdenite

(a) A band of galena and sphalerite fringed by calcite-altered dolomite containing fragments of pyrite. It is uncertain if the calcite rim is related to the galena-sphalerite (b) Molybdenite infill in a quartz vein hosted by K-feldspar altered Ekmαι sandstone.

Intrusive rocks

Approximately 2.5% (2,266m) of drill core was positively identified as being of igneous origin, the majority of which was encountered in drill stations KL30 – KL44, adjacent to the Grasberg Igneous Complex contact zone (see Chapter 2). The igneous rocks are locally difficult to identify due to penetrative garnet alteration. A limited number of igneous rock samples were collected and their composition identified by petrography as monzodiorite and hornblende diorite. Weakly altered examples of monzodiorite are composed of 30-40% evenly distributed 5mm plagioclase phenocrysts and 5-10% phlogopite phenocrysts in a very fine-grained matrix (Plate 3-9). Both the fragment and intrusion are crosscut by biotite in the form of fracture selvage alteration whose colour changes from dark to pale brown across the sediment-intrusion contact. Monzodiorite was found in contact with pyroxene and amphibole-altered rocks while red garnet and brown biotite fracture selvage alteration was found crosscutting monzodiorite (Plate 3-9a, b). Hornblende diorite is found in only one locality at the western end of the deposit in a 15m intersection from 385-400m depth in drillhole KL42-06. The rock is grey to black and contains 10% 1-2mm hornblende and 1-2% 1-2mm brown mica phenocrysts. The hornblende phenocrysts are strongly green-brown pleochroic (Plate 3-10b) and weakly aligned. Phenocrysts are black in unaltered zones of the rock varying to green-grey where they are near bands of quartz alteration. Adjacent to quartz alteration the hornblende is replaced by talc and within the bands they are replaced by fine-grained quartz (Plate 3-10a).

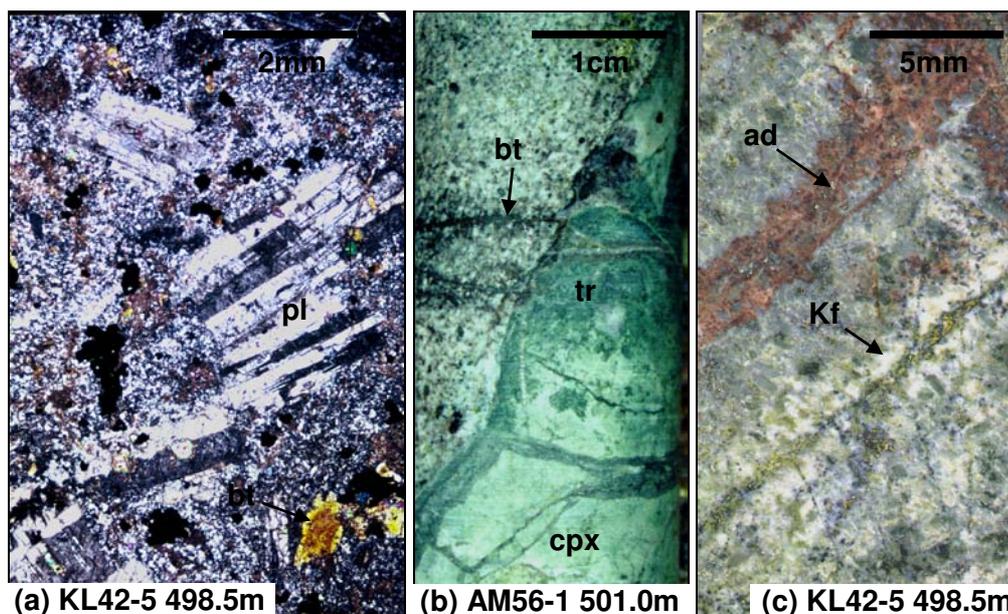


Plate 3-9 Visible and microscopic textures of common alteration effects in monzonite

(a) Photomicrograph of monzodiorite texture showing large plagioclase phenocryst in a fine-grained K-feldspar groundmass which appears to locally overprint an earlier phase of clinopyroxene alteration. (b) Clinopyroxene-tremolite skarn intruded by monzodiorite. Biotite veins crosscutting both the intrusion and the altered fragments are darker brown in the intrusion than in the skarn. The intrusion has exploited the same fracture as tremolite selvage alteration. (c) Selvage accumulations of red garnet (andradite) and K-feldspar along parallel fractures in monzodiorite.

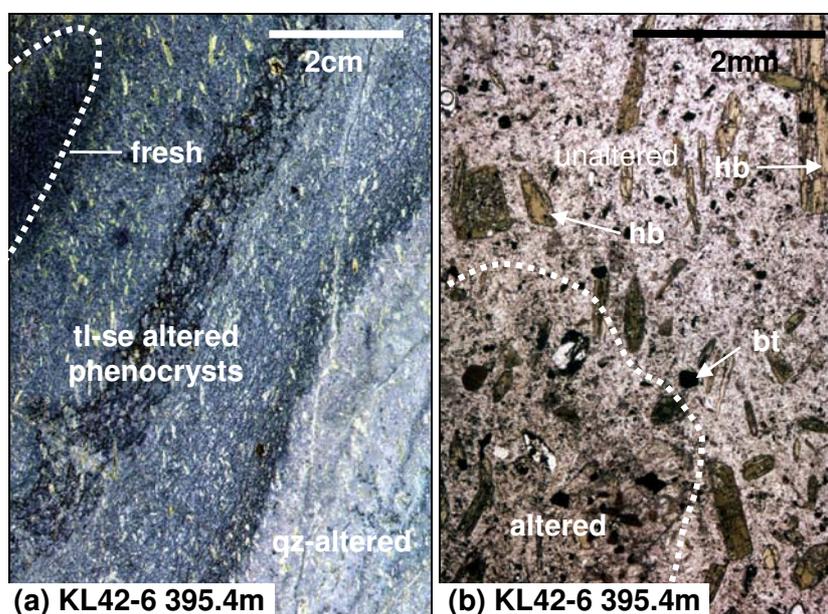


Plate 3-10 Visible and microscopic textures of diorite

(a) A band of white quartz is accompanied by a halo of talc alteration of hornblende phenocrysts in diorite. A patch of unaffected rock at upper left illustrates the original texture. (b) Photomicrograph of the diorite texture, to the top right the phenocrysts are unaffected by hydrothermal alteration.

3.2 INTERPRETATION OF KUCING LIAR PARAGENESIS

The following discussion begins with correlation of the key Kucing Liar hydrothermal mineral assemblages with recognised alteration assemblages that are related to porphyry-related mineralisation and places them in paragenetic context, while the second part examines the conditions of the hydrothermal system based on the key assemblages recognised in the system. There are a large number of minerals developed in Kucing Liar wall rocks that have highly variable chemistry.

Classification and inter-relationships of Kucing Liar mineral assemblages

The alteration assemblages from Kucing Liar rock samples form a complex series of relationships. The complexities are increased by lithological control of alteration where certain minerals and associations only appear in certain wall rock types (Chapter 2). Not all of the relationships are present in every sample, necessitating an approach whereby observed relationships are integrated to form a generalised sequence. There are some issues remaining where key relationships have not been observed, however, the results presented here are considered a good approximation of the paragenetic history for Kucing Liar. The hydrothermal minerals have been grouped into four broad assemblages that relate to four distinct paragenetic stages based on broad temporal relationships. Group I is characterised by a progression of calcite \pm magnetite, clinopyroxene \pm plagioclase, garnet, humite-forsterite. The clinopyroxene \pm plagioclase has two distinct styles that are lithologically-controlled. Group I is overprinted by serpentine after humite-forsterite and tremolite-actinolite after clinopyroxene \pm plagioclase, but not where it occurs as hornfels. Group II is an association of green phlogopite, K-feldspar \pm biotite and magnetite. Group II magnetite is overprinted by tremolite-actinolite but tremolite-actinolite is overprinted by biotite, a convoluted relationship which will be discussed further below. Group III is an association of quartz \pm muscovite \pm talc and anhydrite.

Group I

A fundamental issue concerning Group I is whether or not hornfels-like alteration characterised by hedenbergite \pm plagioclase alteration of calcareous shale is coeval with diopside \pm garnet in limestone. Each association has different clinopyroxene compositions as well as different plagioclase abundances. Both associations are accompanied by garnet though there is a distinct difference where garnet in hornfels is consistently red, indicating high Fe-content and andradite compositions, while garnet in skarn varies from green to orange-coloured, representing a larger variation in composition from andradite to grossular. An alternative explanation to contemporaneous development of these two assemblages is that the hedenbergite \pm plagioclase formed first in calcareous shale and was overprinted by K-feldspar \pm biotite while adjacent limestone rocks were altered to diopside \pm garnet. However, green phlogopite has overprinted clinopyroxene \pm garnet and was in turn overprinted by K-feldspar, establishing that K-feldspar \pm biotite is not equivalent to clinopyroxene \pm garnet. Green phlogopite is also overprinted by tremolite-actinolite, and is also consistently associated with calc-silicate alteration rather than other potassic minerals, indicating it is more probably part of Group I. It is therefore maintained that the progression of Group I is calcite \pm magnetite \rightarrow clinopyroxene \pm plagioclase \rightarrow garnet \rightarrow humite-forsterite \rightarrow phlogopite \rightarrow serpentine and finally tremolite-actinolite.

Calcite \pm magnetite, diopside \pm plagioclase and garnet can be described as calcic skarn due to the significant amounts of diopside-andradite within the required composition ranges, while forsterite-humite alteration is more strictly defined as magnesian skarn and retrograde alteration is the term generally used to refer to the formation of hydrous mineralogy (i.e. serpentine and tremolite-actinolite) in pre-existing skarn (Einaudi *et al.*, 1981). These could equally be referred to as anhydrous and hydrous, or prograde and retrograde skarn. Calcic clinopyroxene skarn replaces limestone and commonly consists of Fe-Ca silicates such as andradite and hedenbergite while magnesian forsterite skarn replaces dolomite and is characteristic of silica-deficient environments (Einaudi *et al.*, 1981). Copper-bearing skarn deposits in porphyry environments

tend to contain andraditic garnet (Einaudi *et al.*, 1981; Meinert, 1998). Skarn deposits typically display a successive pattern of:

- (1) isochemical contact metamorphism accompanying emplacement of the magma
- (2) metasomatism (skarn formation) accompanying crystallization of the magma and evolution of the ore fluid
- (3) retrograde alteration accompanying final cooling of the system (Einaudi *et al.*, 1981).

Early contact isochemical metamorphism develops light-coloured iron-poor calc-silicates, marbles and hornfels. This pattern is repeated in Kucing Liar though the presence of fracture-related selvage alteration in the Ekmai Limestone may indicate that early hornfels was also the product of fluid infiltration rather than isochemical metamorphism. The assemblage clinopyroxene \pm plagioclase is strongly lithologically-controlled as evidenced by the presence or absence of plagioclase, the texture of alteration, and the chemistry of clinopyroxene. The significantly different assemblages of diopside \pm garnet and hedenbergite-plagioclase \pm garnet demonstrate a strong lithological control on early stages of alteration.

The progression of alteration is visible in sandstone layers from samples taken distant from Kucing Liar (see Chapter 2), where the matrix is altered to combination of talc and amphibole, and where clinopyroxene developed at the expense of sand grains. Forsterite can develop either from metasomatism of dolomite and quartz rocks or from alteration of clinopyroxene (Einaudi *et al.*, 1981). Retrogressive alteration involves hydration of reactions involving diopside and forsterite. Tremolite-actinolite and serpentine result from retrograde alteration of different mineral associations in the pre-existing skarn alteration. The dominant trend in retrograde alteration in skarn deposits involves the formation of hydrous silicates that are progressively depleted in calcium as the intensity of alteration increases (Einaudi *et al.*, 1981). Retrograde alteration products typically reflect the composition of the original skarn silicates; epidote, chlorite and

calcite replace grossularite, quartz, iron oxides and calcite replace andradite, biotite-hornblende-plagioclase replace almandine-rich garnet, tremolite-actinolite and eventually talc replaces diopside and serpentine replaces forsterite (Einaudi *et al.*, 1981).

Group II

The sequence of Group II minerals is difficult to interpret due to strong lithological control resulting in a lack of critical relationships. K-feldspar \pm biotite is consistently found to overprint hornfels-like clinopyroxene \pm plagioclase alteration, though there are localised examples of K-feldspar associated with green phlogopite in altered limestone. Group II magnetite is consistently found to crosscut clinopyroxene \pm plagioclase, K-feldspar \pm biotite hornfels and clinopyroxene \pm garnet, humite-forsterite altered limestone. However, magnetite is also consistently overprinted by tremolite-actinolite and occasionally serpentine. Furthermore, localised biotite in limestone-altered rock consistently crosscuts tremolite-actinolite. The simplest interpretation is that a single retrograde alteration phase occurred after potassic-magnetite alteration producing the sequence clinopyroxene \pm plagioclase \pm garnet \rightarrow K-feldspar \pm biotite \rightarrow magnetite \rightarrow serpentine, tremolite-actinolite is equivalent to the sequence calcite \pm magnetite \rightarrow clinopyroxene \pm garnet alteration \rightarrow magnetite \rightarrow serpentine, tremolite-actinolite. However, this is not consistent with biotite overprint of tremolite-actinolite. An alternative interpretation which is preferred here is that there are actually two episodes of tremolite-actinolite alteration, being before K-feldspar \pm biotite and after magnetite alteration.

Alteration mineral assemblages in porphyry systems that consist of quartz, K-feldspar, biotite, anhydrite and magnetite are named the potassic assemblage (*cf.* Lowell and Guilbert, 1970; Gustafson and Hunt, 1975; Hedenquist *et al.*, 1998; Ulrich and Heinrich, 2001a). Potassic alteration of aluminosilicate rocks is one of the characteristics of Au-bearing skarn (Meinert, 1998) and, along with an abundance of hydrothermal magnetite, distinguishes Cu-Au porphyry styles from other porphyry deposits (Sillitoe, 1979). Where potassic alteration assemblages are developed in porphyry-related skarn they generally overprint aluminous skarn hornfels rock types

(Meinert, 1998; Morrison *et al.*, 1999). One explanation for this is that the K originally present in the host rocks (see Chapter 1; Table 1-5) is liberated during skarn formation and may be incorporated into biotite \pm K-feldspar alteration due to circulating fluids. A lithological control on K-feldspar alteration is consistent with observations at Kucing Liar. A second interpretation could be that the potassium has been sourced from the fluids, this is also consistent with the distribution of biotite in high flow zones (see Chapter 4), however, this does not explain the lithological control on potassic alteration. It is likely that the lithological control is a function of the aluminium content from the host rocks (Chapter 1, Table 1-5), which is incorporated into early-formed plagioclase, which in turn is altered to K-feldspar.

Although chemically distinct, magnetite is generally assigned to potassic alteration (*cf.* Lowell and Guilbert, 1970; Gustafson and Hunt, 1975; Hezarkhani and Williams-Jones, 1998) and is ubiquitous in this assemblage in Au-bearing porphyries (Sillitoe, 1997). The connection of K-feldspar \pm quartz veins and magnetite are indicated at Bajo del la Alumbreira where penetrative quartz-magnetite \pm K-feldspar grades laterally into K-feldspar \pm biotite (Ulrich and Heinrich, 2001a). High magnetite content in skarn deposits may be a function of the dolomitic wall rocks, in which Fe-rich calc-silicates are not stable (Einaudi *et al.*, 1981). Elevated magnetite may also indicate the highly oxidized state for the hydrothermal fluids (e.g. Sillitoe, 1997), while the appearance of titanite in quartz veins further constrains the composition of potassic-forming hydrothermal fluids to the boundary between relatively reducing and oxidising conditions described by the assemblage quartz + titanite + magnetite (Xirochakis *et al.*, 2001). Both quartz and magnetite must be derived from the hydrothermal fluids as no major sources of Fe and Si are locally available. The quartz in sandstone may locally provide a source of silica for the development of clinopyroxene and garnet (Chapter 3), though no large-scale dissolution of the quartz sandstone units is evident.

Group III

The Group III assemblage is characterised by quartz alteration accompanied by muscovite and talc and anhydrite alteration, which individually overprint potassic and calc-silicate alteration. Sulphide mineralisation typified by pyrite, chalcopyrite \pm bornite, covellite \pm enargite and galena-sphalerite has been placed within this group, as it appears to be part of the broader assemblage. This lack of any other significant overprint of quartz alteration (other than sulphide) indicates that this mineral assemblage has overprinted all silicate phases. Local relationships indicate that silicification overprints skarn and potassic alteration, though pyrite is more common in magnetite. Timing relationships between anhydrite and quartz are not commonly observed though in some cases show that anhydrite overprinted quartz and muscovite alteration. Anhydrite is consistently overprinted by pyrite. Group III also includes covellite \pm enargite \pm pyrite mineralisation which is most prevalent as infill in vuggy quartz alteration. Less abundant mineralisation includes bornite, digenite accompanying chalcopyrite and nukundamite and chalcocite accompanying covellite. A rare assemblage consisting of nukundamite \pm chalcocite is also recognised associated with alteration dominated by muscovite rather than quartz. Locally penetrative galena-sphalerite pyrite developed at the margins of the main metasomatic zone. Some molybdenite is also recognised as forming after anhydrite and overprinting covellite \pm pyrite \pm enargite.

The assemblage quartz \pm muscovite \pm pyrite is characteristic of phyllic alteration of porphyry deposits and, in conjunction with locally massive pyrite, also characterizes the “silica-pyrite” alteration found in skarn systems (Einaudi *et al.*, 1981). Silica-pyrite may replace skarn, but also replaces limestone as massive irregular bodies, mantos, or steep structurally controlled breccia pipes (Einaudi *et al.*, 1981). This is consistent with Kucing Liar, where both quartz alteration and massive pyrite are found in both skarn and unaltered limestone. A direct correlation exists between sericitic (phyllic) alteration of the pluton and the formation of silica-pyrite in adjacent skarn (Einaudi *et al.*, 1981). Covellite \pm pyrite \pm enargite mineralisation is one of the characteristic assemblages that define high sulphidation mineralisation, which is commonly pyrite-rich and typified by enargite, luzonite, digenite, chalcocite, covellite and nukundamite (*e.g.*

Sillitoe, 1999; Inan and Einaudi, 2002). Although high sulphidation mineralisation is generally confined to advanced argillic alteration zones typified by quartz, alunite, kaolinite or diaspore (*cf.* Hedenquist *et al.*, 1998), at some localities it extends into the sericitic (phyllic) zone, commonly zoning from advanced argillic to phyllic, which subsequently grades downwards into potassic alteration (Sillitoe, 1999). This is the case at Kucing Liar where high sulphidation mineralisation is generally formed in quartz-pyrite-muscovite alteration, though its independence from phyllic (silica-pyrite) alteration is recorded in the occurrence, albeit rare, of covellite in calc-silicate skarn. A significant problem with the Kucing Liar paragenesis is the relationship between chalcopyrite and covellite mineralisation. The sequence of development is not rigidly constrained, as the timing of sulphide minerals is commonly questionable, due to ambiguous sulphide growth textures and almost complete absence of rocks containing both of the main Cu-bearing phases. Both Cu-bearing sulphides are associated with pyrite, though chalcopyrite tends to be developed in association with coarse, brassy pyrite rather than fine pyrite.

Petrologically defined conditions of the Kucing Liar hydrothermal system

The early stages of the paragenesis indicate moderate to high temperatures and near neutral pH, while the later stages demonstrate a significant lowering of temperatures and pH conditions. Solutions associated with quartz monzonite will be nearly neutral and enriched in iron relative to magnesium (*cf.* Einaudi *et al.*, 1981).

Studies of numerous skarn deposits around the world indicate temperatures of formation for prograde skarn (Chapter 2) between 400°C and 650° and that there is a relationship between temperature and pressure where lower pressures lower the temperature limits of skarn formation (Einaudi *et al.*, 1981). Skarn minerals (monticellite) from the DOM deposit have high temperature (~700°C) and high salinity fluid inclusions (Meinert *et al.*, 1997), while Big Gossan and EESS skarn minerals, preserve much lower temperature fluid inclusions (300-500°C) of more moderate salinity (Meinert *et al.*, 1997).

Potassium silicate alteration in porphyry-related hydrothermal systems is generally believed to form during initial cooling of magmatic brines from 600° to 400° (*cf.* Einaudi *et al.*, 1981; Sillitoe, 1997; Hedenquist *et al.*, 1998). The appearance of titanite in the quartz veins may have a bearing on the composition of hydrothermal fluid. The assemblage titanite + magnetite + quartz is generally thought to mark the boundary between relatively reducing and oxidising conditions and likely more common in relatively Fe-rich bulk compositions and for decreasing temperature and pressure conditions (Xirochakis *et al.*, 2001). The elevated magnetite reflects the highly oxidized state of the magma from which gold-transporting fluids were derived (Sillitoe, 1997).

Extensive late replacement of prograde skarn by retrograde skarn and silica-pyrite presumably reflects the presence of a long-lived, sulphur rich hydrothermal system operating in a highly fractured, hence permeable, environment (Einaudi *et al.*, 1981). A decrease in temperature, oxidation by groundwater influx and low pressure boiling can all contribute to the generation of hydrothermal fluids that are out of equilibrium with plutons and skarns (Einaudi *et al.*, 1981; Meinert *et al.*, 2003), which leads to the development of retrograde alteration. Temperatures for retrograde alteration generally range from 450° to 300°C (Einaudi *et al.*, 1981). More specifically, serpentinisation of forsterite-bearing magnesian skarn (Chapter 2) in low-pressure environments implies temperatures less than 420°C (Einaudi *et al.*, 1981). The more pervasive retrograde replacement of magnesian skarn compared to calcic skarn reflects the instability of forsterite in water-rich fluids in temperatures below 400°C (Einaudi *et al.*, 1981).

The presence of muscovite and quartz-covellite indicate mildly acidic conditions and moderate temperatures. Sericite-stable alteration assemblages are associated with cooler, less saline water (Hedenquist *et al.*, 1998). However, the absence of kaolinite or alunite may indicate that highly acidic conditions were not achieved. The contrasting mineralisation assemblages recognised in Kucing Liar indicates different fluid conditions as covellite is related to slightly acidic conditions and high sulphidation stages while chalcopyrite deposits under more neutral acidity and intermediate sulphidation states (e.g. Einaudi *et al.*, 2005).

4 Structural setting

The following section documents the large-scale context of the Kucing Liar mineralisation, as reflected by the distribution of the major hydrothermal minerals. Routine logging of all drill core included identification of lithology and estimation of individual mineral abundances for all core samples (Appendix IV). During routine exploration drilling, sample intervals were assigned by mine geologists at regular lengths of 3m but made shorter where significant changes in geology were present (N. Wiwoho, pers comm.). Technicians then split the core using a screw press to produce a sample ready for assay. A short length of drill core (10-20cm) was removed from each assayed interval prior to splitting, and retained, producing an archive of “skeleton” core. The drill holes were logged in two phases from Sept.-Nov. 1997 and June-Sept. 1999. During the first phase, continuous (“full core”) that had been split for sampling was utilised, while during the second period only skeleton core was examined due to the much shorter time required to examine and log a single hole. The second period of logging revisited many of the drill holes logged on the first occasion, enabling a comparison between logs of continuous core versus skeleton core. No major differences were found comparing the data from the two different sample collections.

The structural setting has been interpreted independently for this research program from the skeleton core logged by this author to develop detailed cross sections through the mineralised zone. Polygonal outlines developed from data within individual drilling stations for major stratigraphic contacts each of the major mineral assemblages honour the position of contacts on drillhole traces and were converted into wireframes. Three-dimensional surfaces representing the major stratigraphic contacts have been derived from correlation of stratigraphy between radial drill fans (Chapter 1), and are used to illustrate the structural setting of mineralisation. Visual estimates of mineral abundances in drill core samples (see Appendix V) were also analysed in three dimensions using Vulcan and Surpac mine-environment software. Cross sections of these surfaces and isosurfaces are the primary method used to interpret structural controls on fluid flow.

4.1 STRATIGRAPHIC AND FLUID FLOW MODELLING

The main units of interest in the Kucing Liar deposit are the Ekmai and Waripi Limestones, and less importantly the Faumai Limestone, the Sirga Sandstone and the Kais Limestone. Each of these units is unique with respect to the overall sequence. Their contacts are important in identifying stratigraphical position as well as the location of fault zones. The positions of the distinctive marker horizons have been correlated between drill stations to form three-dimensional surfaces and are combined with the 3D distribution of hydrothermal alteration to provide as full a picture as possible of the structural history of the Kucing Liar system.

4.1.1 Lithological distribution

Stratigraphic sequence recognition

While the original composition and texture of wall rocks could be identified for type samples in KLS1-1 and KLS3-1, much of the sequence is affected by hydrothermal alteration. As the wall rocks in the mineralised zone are, by definition, extensively replaced, identification of texture retention during alteration is an important step in correctly assigning stratigraphic position of host rocks. Textural retention and lithological control of mineralogy is a feature of hydrothermal mineral development at Kucing Liar, which, in combination with unique sequences and marker horizons, allows stratigraphic characterisation of the altered sequences in the main mineralised zone. As the sequence of lithology has been established, deviations from the expected lithology identify the components added during modification. Each type of alteration displays a continuum of modification that can be traced from original texture and composition in KLS1-1 and KLS3-1 through to total replacement of the original rock within the mineralised zone.

Textural retention during alteration

Fundamentally, there are only three sedimentary rock types, i.e. limestone, sandstone and shale, which host Kucing Liar alteration and mineralisation, each of which can be identified either by a distinctive texture or a particular alteration mineralogy (Plate 4-1).

The base of the mineralised zone is marked by the Ekmai Sandstone which is a relatively homogeneous unit with monotonous white K-feldspar \pm muscovite \pm covellite \pm pyrite. In some drilling, sharp contacts between K-feldspar and quartz-dominant alteration were observed. The deepest penetration of the Ekmai Sandstone (in KL42-3) intersected a section of clinopyroxene-garnet-K-feldspar-biotite hornfels that is very similar in appearance to altered sections of the Ekmai Limestone. The lower contact with the Ekmai Sandstone marks a change from underlying homogeneous sandstone to very fine-grained shale and is distinctive in altered sequences where the overlying zone is typified by a 5-10m zone of abundant green or brown-red garnet and magnetite in the lower Ekmai Limestone. The main body of the Ekmai Limestone is generally homogeneous and typified by very fine-grained hornfels that may be green (pyroxene-feldspar), white (K-feldspar) or brown (K-feldspar \pm biotite). Where present, the Ekmai shale is altered to a distinctive brown K-feldspar \pm biotite rock and contains a quartz stockwork that is distinct from sheeted vein arrays hosted in the underlying Ekmai Limestone and which are absent from overlying Waripi Limestone (zone 8 in Plate 4-1). This unit is not present throughout the mineralised zone, but it is definitive.

The Waripi Limestone overlies the Ekmai Limestone and typically contains a number of different zones where intersected in the deposit. The lowermost zone commonly hosts thick concentrations of magnetite or garnet that form sharp contacts with clinopyroxene-plagioclase or K-feldspar-biotite altered shale. This zone is typified by intense brecciation with an abrupt lower contact to the Ekmai Limestone and a transitional contact to overlying skarn alteration (zones 5 and 6 in Plate 4-1). The lower contact with the Ekmai Limestone represents a change from very fine-grained black shale to fine-grained grey peloid limestone and as such is easily recognised. Diopside skarn occurs above the magnetite breccia /garnet zone and has been overprinted by orange humite-forsterite, dark green phlogopite, green tremolite-actinolite or thin magnetite zones (zone 4 in Plate 4-1). The upper contact of skarn and accompanying alteration is commonly sharp, in some cases (zones 3 and 4 in Plate 4-1) defined by a thin concentration of garnet accompanied by sphalerite and galena mineralisation. A zone of calcite alteration above this contact is

gradational to grey dolostone (zone 3 in Plate 4-1). This is succeeded by the upper Waripi sandstone member, which is typically intensely altered to vuggy quartz and contains metre-scale lenses of pyrite. This alteration does not typically extend outside the quartz layer, which is overlain by thin K-feldspar-biotite hornfels developed in thin shale.

Marker horizons

The precise position of the upper Waripi Limestone contact with the Faumai Limestone is difficult to recognise as the thin (~5m) laminated sandstone layer that marks the top of the Waripi Limestone is commonly not observed due to the scale of sampling (see Appendix V). However, the approximate location of the contact is indicated by the location of the much thicker (~50m) upper Waripi sandstone member and its accompanying, easily identifiable shale layer (zones 2 and 12 in Plate 4-1). The position of the Idenberg Fault Zone can be identified in many drill holes due to variation from the normal stratigraphic sequence. The Ekmai Sandstone is known from regional studies to be 600m thick (Chapter 1). Drill holes oriented from near vertical or toward the northeast either intersect thick monotonous sandstone or porphyry. However, drill holes oriented toward the southwest do not follow the expected sequence, indicating the presence of a fault. The Idenberg Fault Zone is manifested either as an abrupt change in lithology, which may be altered sandstone to altered limestone, commonly separated by 5 to 10m of magnetite ± phlogopite ± tremolite ± chalcopyrite ± pyrite, or as a broader zone characterised by fragmental rocks altered to magnetite ± quartz ± pyrite (zone 9 in Plate 4-1). In many instances the alteration mineralogy does not allow specific identification of the texture or lithology of the precursor. Garnet, magnetite, quartz and pyrite are all associated with extensive fragmentation of the host rocks (Chapter 3) and it is interpreted that intense development of these minerals indicates the presence of a fractured zone that represents the position of a fault (Plate 4-1).

Out-of sequence limestone has been encountered beneath the Ekmai Limestone on the southwest margin of the main mineralised zone. A thick magnetite zone commonly occupies the contact between normal stratigraphy and out-of-sequence limestone (zone 9 in Plate 4-1). The limestone

is variably altered with increasing intensity with depth from calcite to calcite \pm magnetite with minor humite development and finally to clinopyroxene and humite skarn overprinted by retrograde tremolite-actinolite and serpentine (zones 10 and 11 in Plate 4-1). The distinctive upper Waripi sandstone member is occasionally recognised in deeper drilling intersections within this zone of altered limestone from the same distinctive quartz and potassic hornfels alteration identified above the mineralised zone (e.g. zone 12 in Plate 4-1). Additionally, sandstone of similar thickness to the upper Waripi sandstone member but containing a shale layer in the middle rather than at the top is identified in a small number of holes and is interpreted to be the Sirga Sandstone. Where recognised, the Sirga Sandstone is quartz-garnet altered with minor lenses of pyrite. Recognition of these distinctive layers in deeper drilling confirms the presence of a fault zone and allows the magnitude of displacement to be measured.

Stratigraphical interpretations indicate that the Kucing Liar deposit can be divided into two parts with similar sequences separated and offset by the Idenberg Fault Zone. The position of this fault is indicated by departure from the ideal stratigraphic sequence (Figure 4-1). The rocks above the fault consist of well-constrained stratigraphic sequence of Waripi Limestone, Ekmai Limestone and Ekmai Sandstone and will be referred to as the main mineralised zone. The footwall stratigraphy is less well defined due to limited drilling. The general impression of the structure at Kucing Liar can be gained by comparing the sequences intersected at different drill stations along the strike of the system (Figure 4-1). The stratigraphy of Kucing Liar is generally consistent along strike though there is a significant change in the structure at station KL44, which marks the western extent of mineralisation (Figure 4-1). Below the fault zone the Waripi Limestone and Faumai Limestone are recognised from the relative position of a second intersection of the upper Waripi sandstone member (Figure 4-1). The Sirga Sandstone is also recognised in KL44-2 adjacent to the main mineralised zone but separated from it by a porphyry intrusion that occurs in the Idenberg Fault Zone (Figure 4-1).

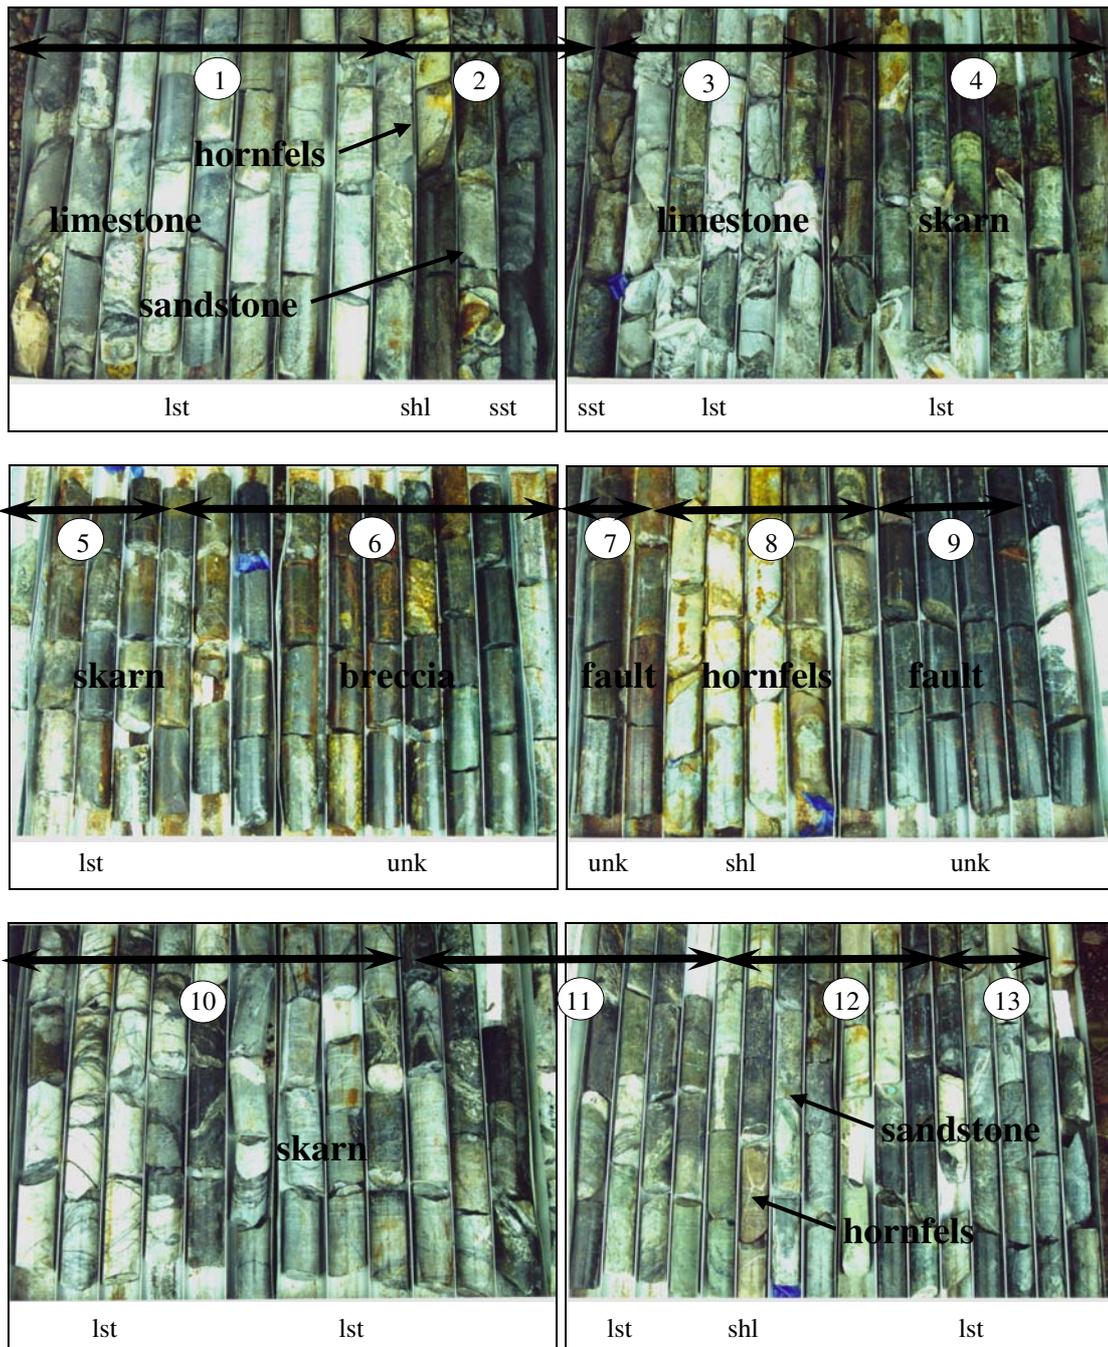


Plate 4-1 An example of lithological sequence commonly found in faulted regions

Drill core samples from KL40-07 (Figure 4-1) representing assay intervals that are generally 3m long. The total depth of the hole is 911m (lst = limestone, shl = shale, sst = sandstone, unk = unknown). Zones: 1–carbonate altered limestone, 2–quartz altered sandstone including feldspar + biotite altered shale, 3–carbonate altered limestone, 4–pyroxene-garnet-phlogopite-tremolite altered limestone, 5–pyroxene altered limestone plus magnetite-pyrite altered zones, 6–magnetite plus minor pyroxene altered limestone, 7–magnetite altered zone, 8–feldspar±biotite altered shale, 9–magnetite altered zone, 10–calcite±magnetite±humite altered limestone, 11–pyroxene altered limestone, 12–pyroxene and quartz altered sandstone including feldspar±biotite altered shale, 13–calcite-magnetite and humite-forsterite altered limestone.

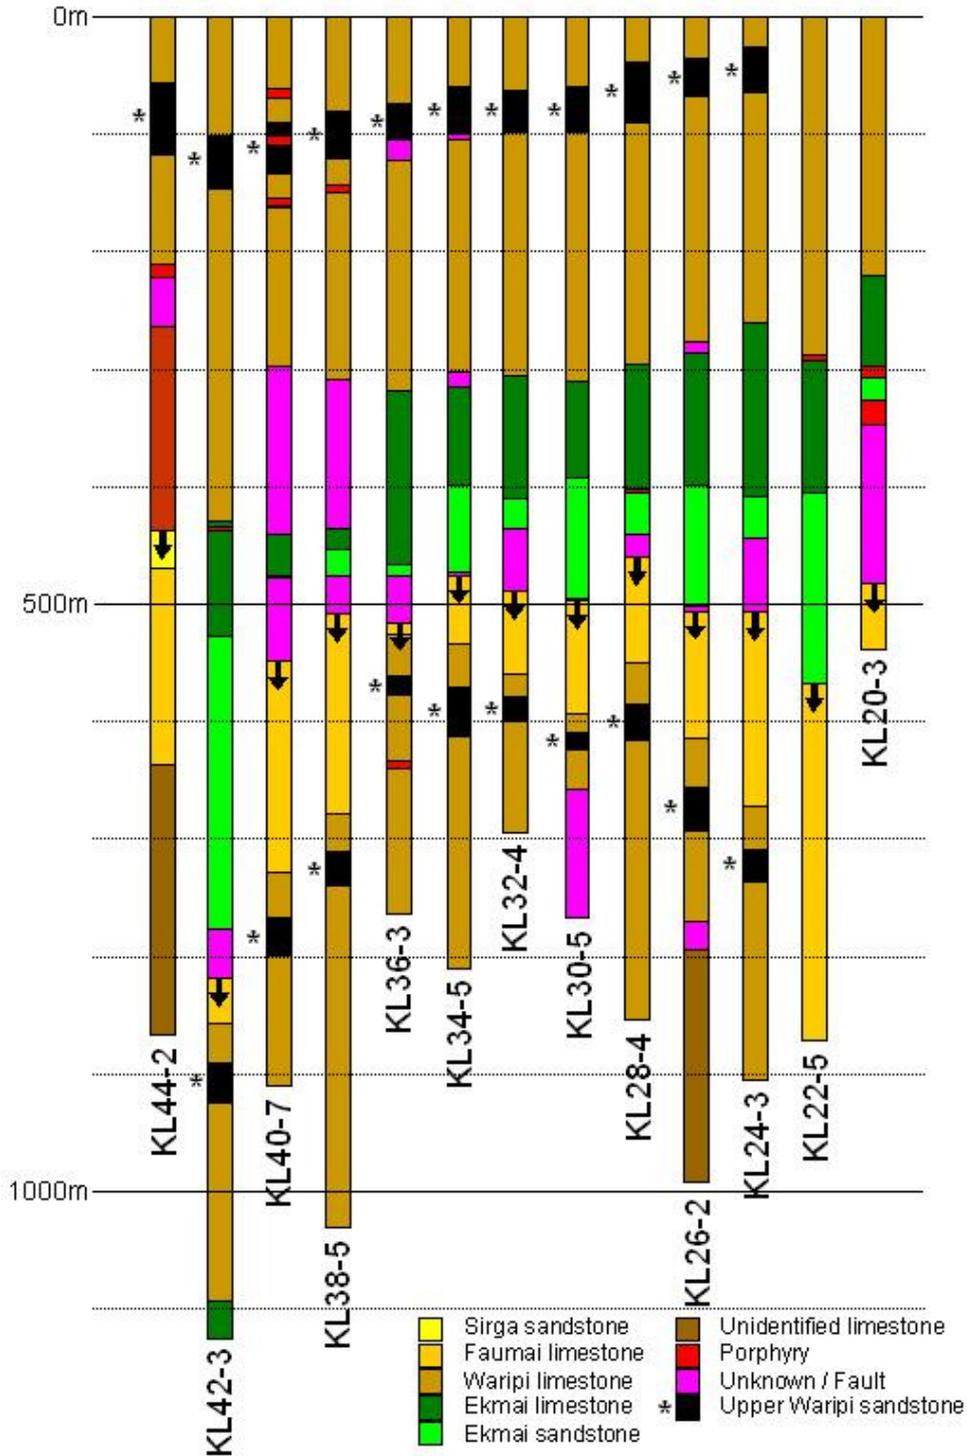


Figure 4-1 Stratigraphic patterns identified in drilling

Stratigraphic interpretation of drilling from each drill station is illustrated using holes that dip approximately 60° toward southwest, though significantly steeper holes (KL30-5, KL42-3) were included as there were no other satisfactory holes from these stations. The position of the upper Waripi sandstone member relative to the drill collars illustrates continuity of stratigraphy and the basic orientation of strike. An arrow marks the start position of out-of-sequence stratigraphy. See Appendix I for the position of each of these drill holes. There is a large amount of vertical exaggeration as the holes are spaced approximately 100m apart (see Chapter 1), meaning the holes represent 1,200m of strike length.

Large-scale geometry

The Waripi and Ekmai Limestone units, as well as upper sections of the Ekmai Sandstone, dominate the stratigraphy of the main mineralised zone northeast of the Idenberg Fault Zone (Figure 4-2, Figure 4-3). Much of the rock mass intersected on the southwest side of the Idenberg fault zone is undifferentiated limestone at higher levels, though it is likely to be the Kais Limestone, due to the local recognition of the Sirga Sandstone (Figure 4-2). However, the recognition of the upper Waripi sandstone member in much of the deeper drilling allows some reconstruction of the geometry of stratigraphy in the footwall of the Idenberg Fault Zone. Bedding strikes consistently at $\sim 290^\circ$ in this part of the system. Unit boundaries dip north but are concave upwards directly adjacent to the Grasberg Igneous Complex, which is intersected at the centre and northwest end of the deposit and has a near vertical contact with host rocks (Figure 4-3). Although data on the southwest side of the Idenberg Fault Zone are scarce, the strike of the upper Waripi shale/sandstone marker is observed to be similar to that on the northeast side. The Ekmai Limestone is thicker in the southeast than in the northwest, while the Waripi Limestone is thicker in the northwest than in the southeast (Figure 4-3). Thickening is coincident with inflections in the strike of the Ekmai Limestone. The distribution of marker horizons in cross section, especially the upper Waripi shale/sandstone marker, illustrate that total vertical separation across the Idenberg Fault Zone is $\sim 600\text{m}$, north side up relative to south (Figure 4-3). The Idenberg Fault Zone has an offset geometry when viewed in cross section, plan and long section (Figure 4-3). The 290° striking segments are 50-100m thick, while vertical, 300° striking segments are only 5-10m thick.

(Overleaf): Figure 4-2 is a series of sections of each cross section studied during this research program. They are included to demonstrate the continuity of stratigraphy as well as the variation in exposure scale for each section. The stratigraphic patterns are derived from projection of drill traces onto flat page and so may not be strictly accurate due to non-planar drill traces. The relative position of the shale horizon marker in the upper Waripi Limestone gives an impression on the scale of displacement across the Idenberg Fault Zone. Stratigraphic unit codes are; Tngk = Kais Limestone, Tngs = Sirga Sandstone, Tngf = Faumai Limestone, Tngw = Waripi Limestone, Kkel = Ekmai Limestone, Kkes = Ekmai Sandstone. Pink shaded areas depict areas where stratigraphic assignment is not possible, while dotted pattern depicts fault breccia zones.

Figure 4-2 Serial sections of Kucing Liar lithology (refer Chapter 1 for section locations)

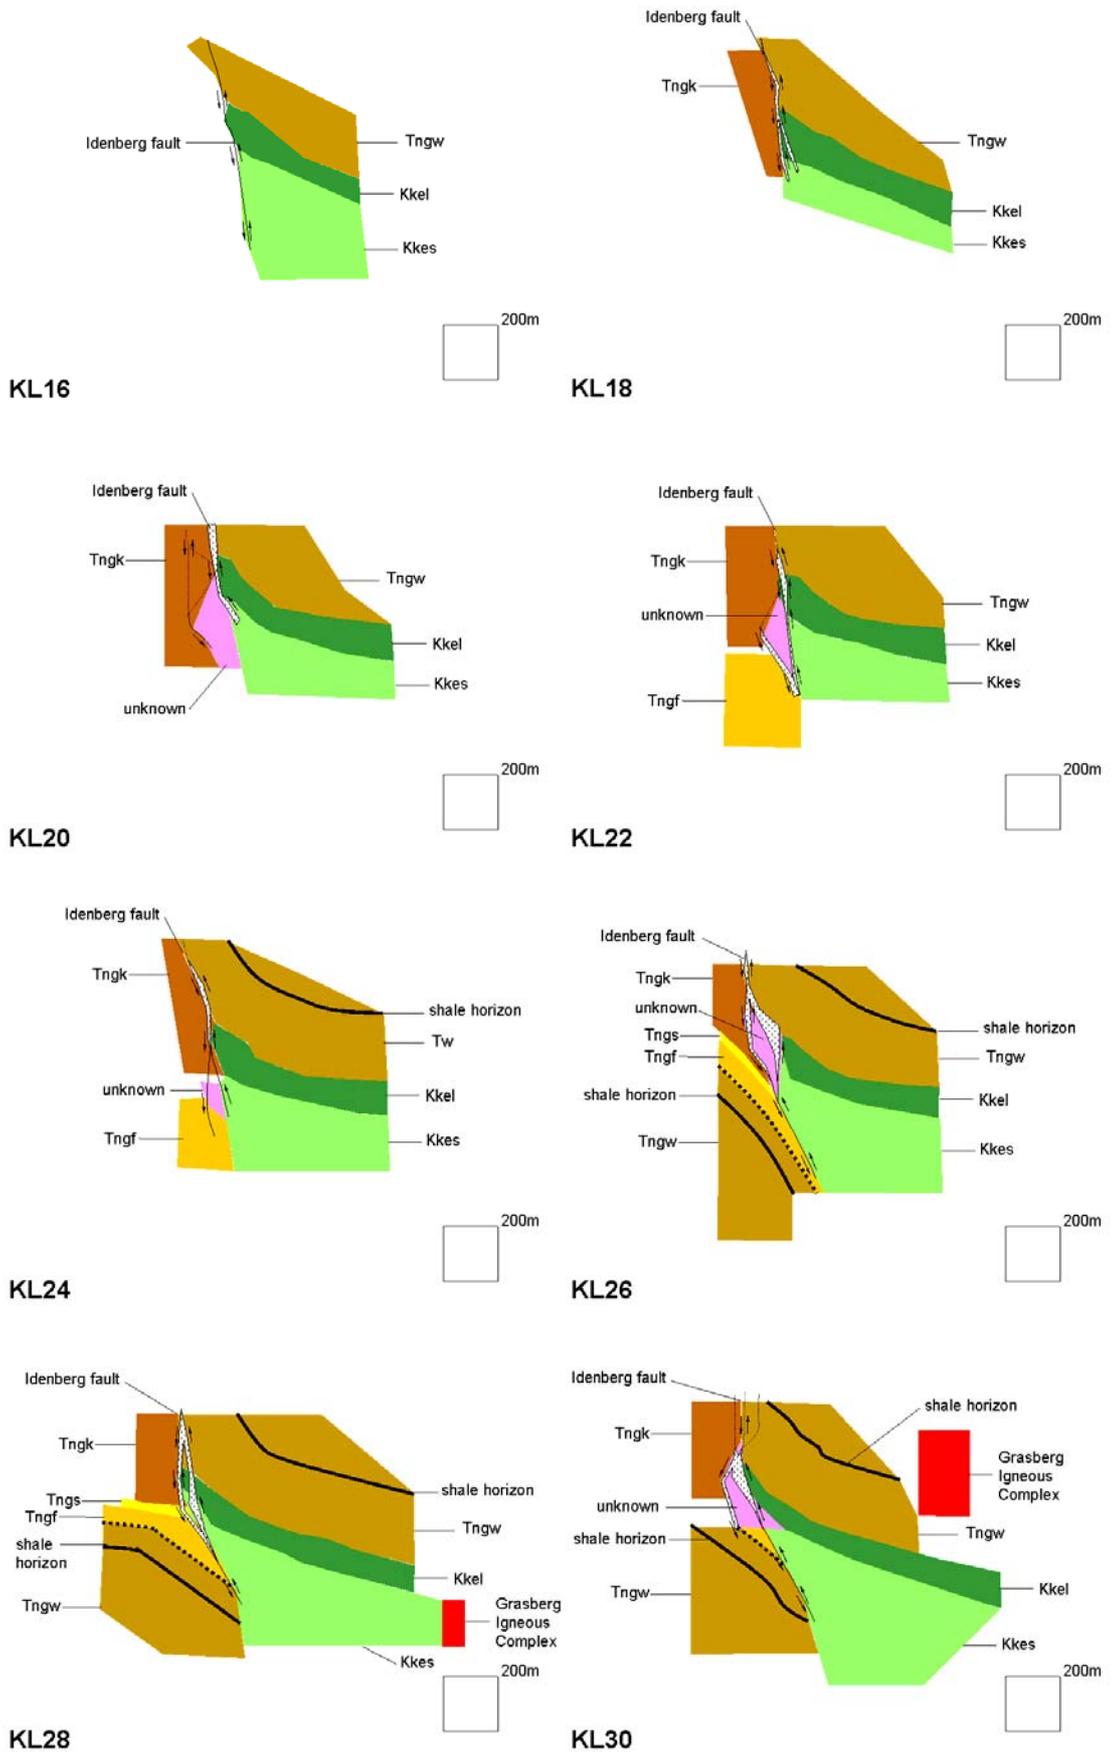


Figure 4-2 Serial sections of Kucing Liar lithology (cont.)


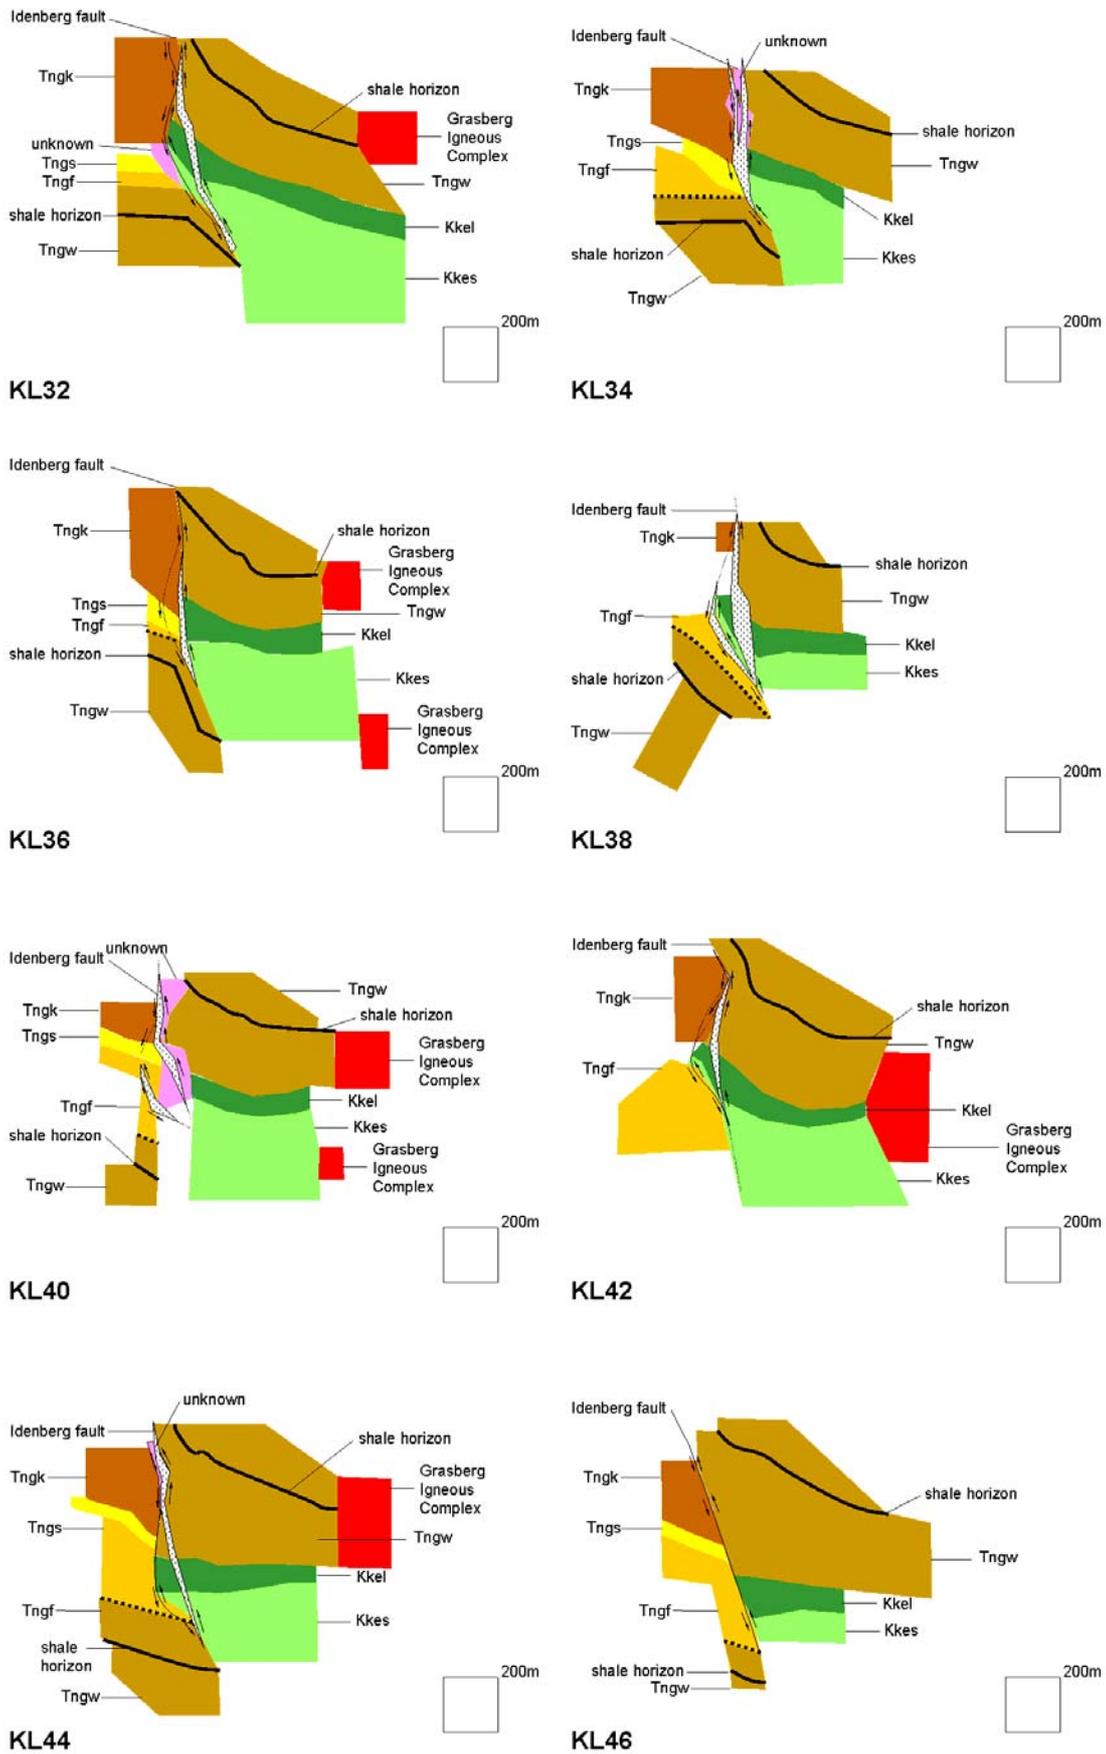


Figure 4-3 Interpretative cross sections of Kucing Liar stratigraphy from wireframes

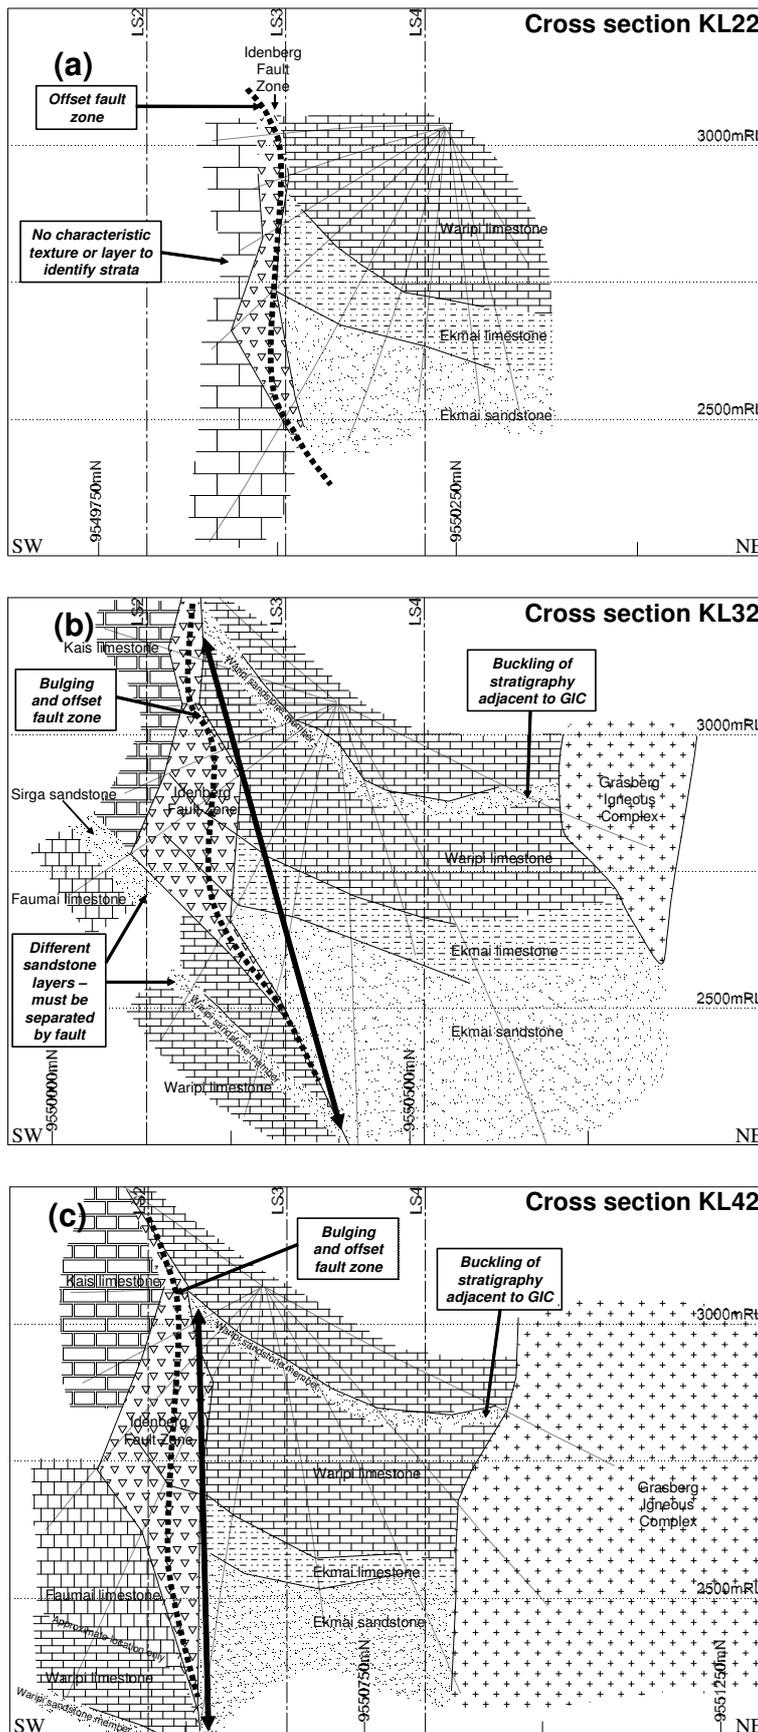


Three representative cross sections selected from the centre and either end of the deposit (spaced roughly 500m apart, see Figure 4-4). Unlike the previous Figure 4-2, the stratigraphic contacts in this figure are not projections but are sections taken from individual wireframes that were interpreted for each unit contact from its real position in each drill trace using 3D mine environment software. The drill traces are projected onto section planes as grey lines. No vertical exaggeration.

(a) A cross section through station KL22 shows relatively simple stratigraphic succession adjacent to a discrete fault offset (dotted line). Due to carbonate alteration and little exposure the exact position of the stratigraphy to the left (southwest) of the Idenberg Fault Zone (IFZ) could not be determined.

(b) A section through KL32 in the centre of deposit shows a much greater exposure of the system. In this section the offset in the IFZ is much more pronounced. More drilling past the IFZ has allowed identification of the upper Waripi shale-sandstone marker horizon and subsequent overall movement on the fault zone (heavy black arrow)

(c) A section through KL42 again shows the IFZ offset and displacement (heavy black arrow), as well as the position of the Grasberg Igneous Complex (GIC). Note the apparent buckling of stratigraphy adjacent to the GIC.

Figure 4-4 Interpretative plan sections of Kucing Liar stratigraphy from wireframes

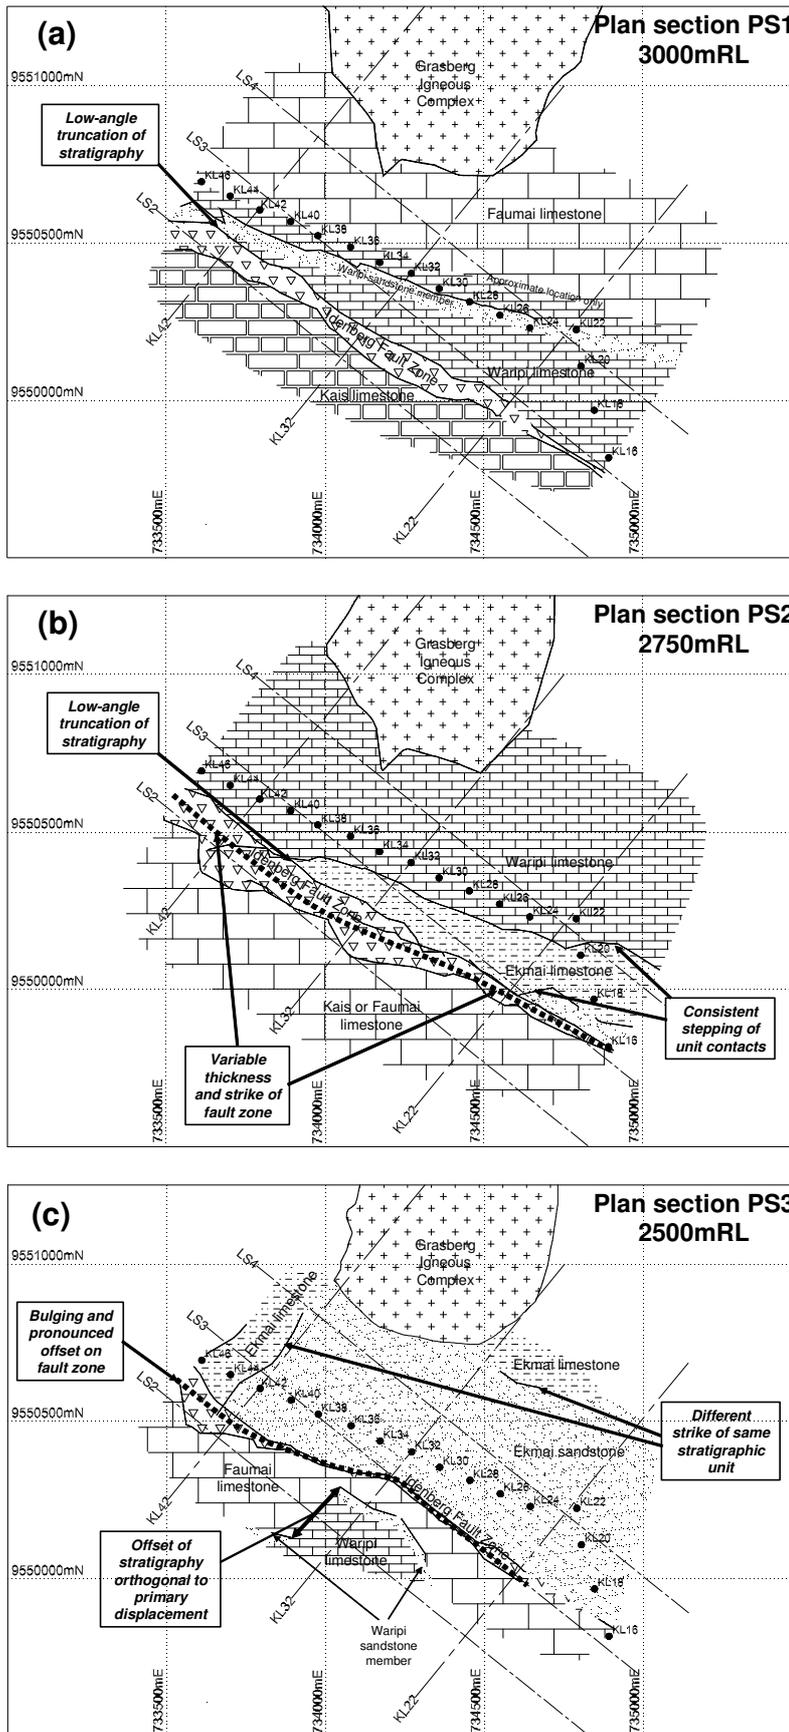


Three representative plan sections spaced 250m apart, see Figure 4-3 for locations. The stratigraphic contacts in this figure were created from individual wireframes that were interpreted from each cross section. The locations of drill stations for each cross section are projected onto the sections for orientation purposes. The outline of the Grasberg Igneous Complex (GIC) was supplied by PT Freeport Indonesia geologist Peter Manning.

(a) A plan section through 3000mRL (above sea level) shows the angular relationship between sedimentary units and the Idenberg Fault Zone (IFZ). The IFZ in this section is relatively simple. The sandstone-shale marker horizon in the Upper Waripi Limestone is shown intersecting the IFZ in the far west.

(b) A section through 2750mRL (above sea level) shows the truncation of the Ekmai Limestone against the IFZ. Also apparent in the east are offsets in the Ekmai Limestone that may be an expression of minor faulting associated with the IFZ. The IFZ shows variable thickness and orientation in this section.

(c) A plan at 2500mRL (a.s.l.) shows a complicated orientation of the Ekmai Limestone and a very narrow but offset IFZ. This section also indicates an offset of the stratigraphy in the footwall of the IFZ which is normal to the main fault zone.



Figure 4-5 Interpretative longitudinal sections of Kucing Liar stratigraphy from wireframes

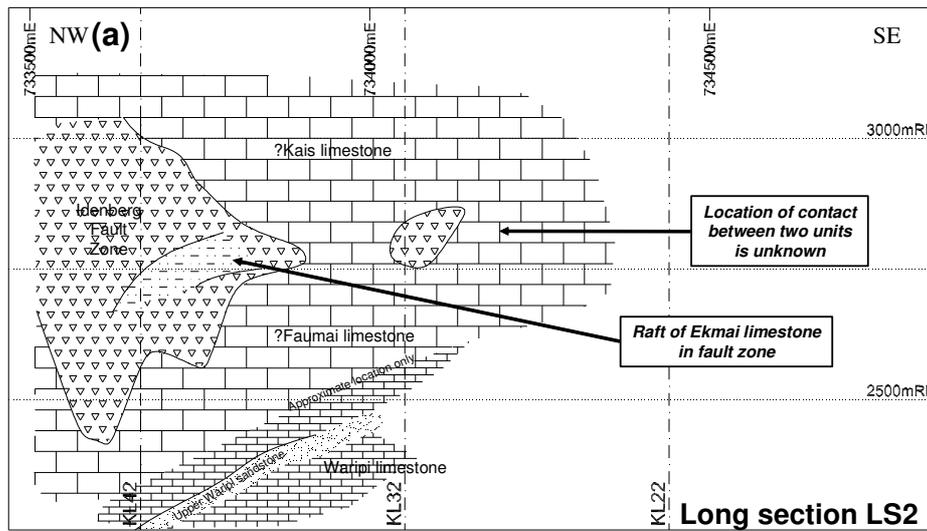

Three representative long sections of the stratigraphic wireframes created from 3D drilling data. Intersections of stratigraphic wireframes with the section plane are indicated by continuous lines. The sections are vertical and orientated

perpendicular to the primary drilling azimuth (see Figure 4-3 and 4-4). (a) Is generally in the footwall of the Idenberg Fault Zone (IFZ) which can be seen in the far left of the section. (b) A section through the middle of the deposit shows thickening of the Ekmai Limestone as well as a bulging offset in the IFZ which is not equivalent to that observed in cross sections in Figure 4-3.

The total displacement across the IFZ is indicated by a thick double-headed arrow. (c) A section close to the GIC (see Figure 4-3) shows relatively simple stratigraphy with minor offsets and thinning.

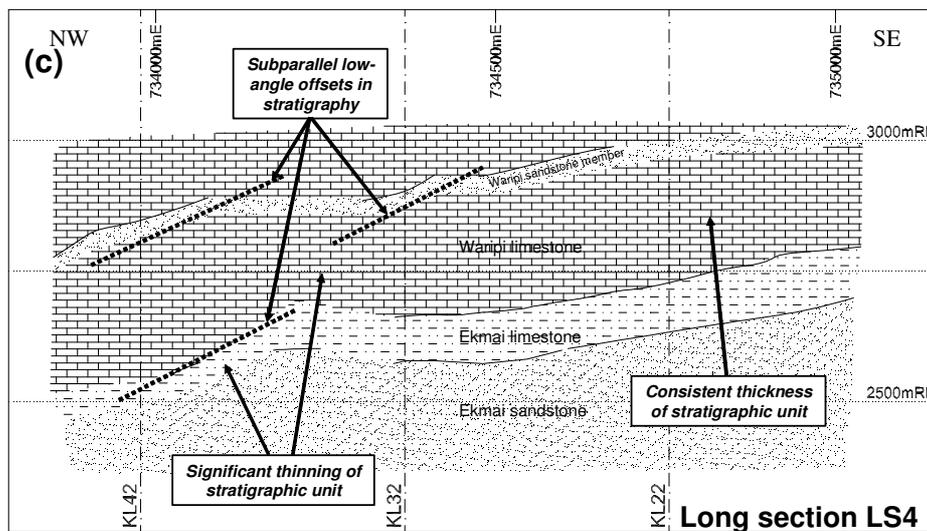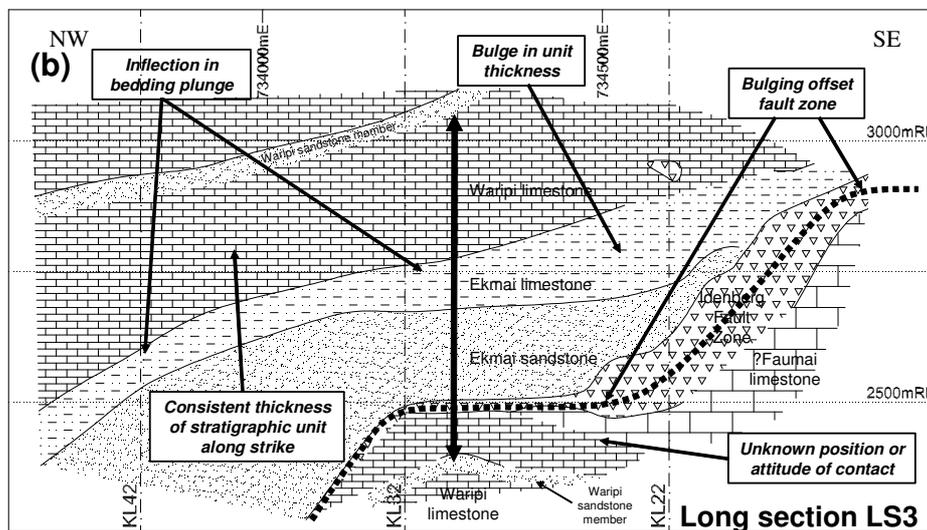


4.1.2 Hydrothermal mineral distribution

This section covers the local-scale controls on fluid infiltration as well as the deposit-scale controls. The structural controls of fluid flow within Kucing Liar are analysed via meso- (hand sample), macro- (single drill hole) and mega-scale (drill fan) patterns of hydrothermal mineral development. Local controls are determined by down hole plots of mineral abundance and lithological data while deposit-scale controls are identified by comparing alteration distribution models with lithological models presented in the previous section.

Patterns of hydrothermal alteration

Fluid flow was not uniform through Kucing Liar wall rocks, as fluids were structurally controlled at various scales. The patterns of mineral distribution are illustrated by down hole logs which display the abundances of each hydrothermal mineral (Figure 4-6). The three examples shown illustrate respectively, the Idenberg fault zone in relatively unaltered hosts (KL32-01), a complex fault system and complicated stratigraphy (KL32-04), and a simple fault system accompanied by simple stratigraphy (KL32-05). KL32-01, KL32-04 and KL32-05 were all drilled toward 219° at 0, 45 and 60° respectively. In KL32-01, sedimentary rocks on the north side of the fault are generally unaltered except for low abundance calcite ± magnetite alteration of the upper Waripi sandstone member that elsewhere commonly contains quartz alteration. KL32-04 was drilled at -45° and intersected two fault zones delineated by zones where the lithology is generally unrecognisable. KL32-05 was drilled at a steeper angle and intersected deeper sections of the Idenberg Fault Zone. Discrete intersections dominated by single minerals extend in length from 5-100m along a drill hole and are commonly 10-20m. Contacts between such zones dominated by different minerals are commonly sharp. Some exceptions include gradual and sympathetic abundance changes between K-feldspar and quartz alteration in the Ekmai Limestone (KL32-04, 350-400m). However, contacts of the K-feldspar-quartz with magnetite-sulphide and clinopyroxene are commonly sharp.

Figure 4-6 Lithological patterns and mineral abundances in representative drill holes

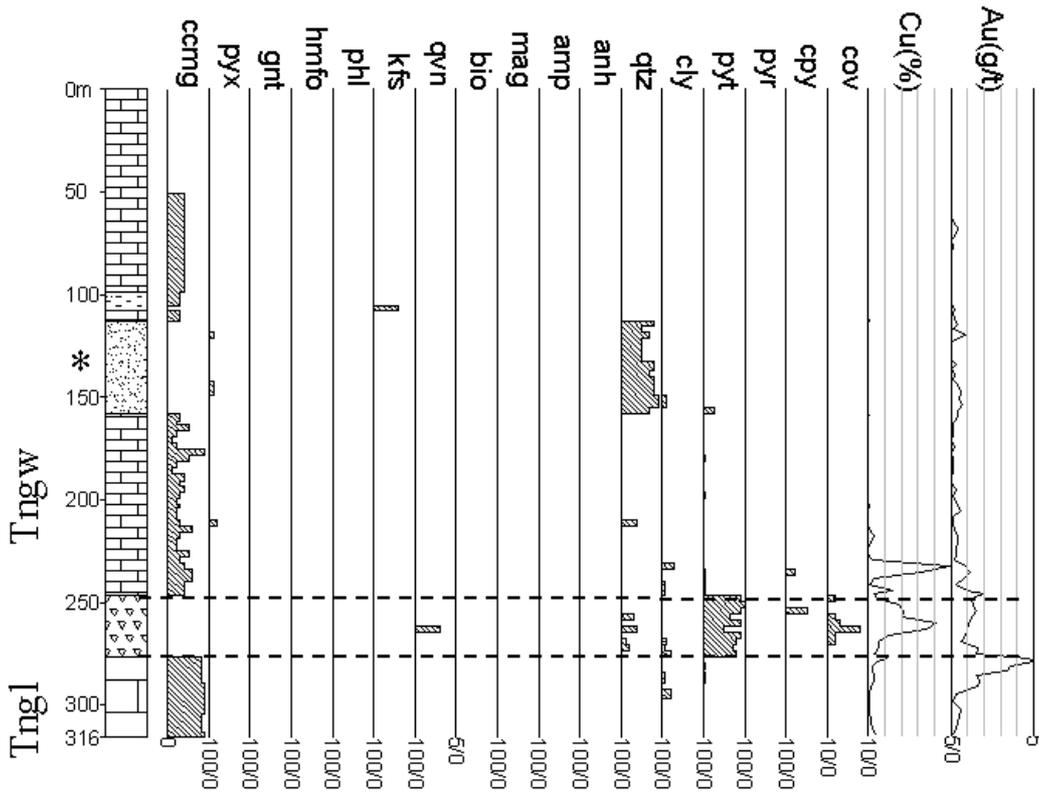


KL32-01 Idenberg Fault in relatively unaltered hosts

This figure is intended to demonstrate three patterns of lithology and alteration encountered in drilling conducted on the same cross section (KL32). See Figure 1-12 for the precise angular relationships between each drillhole. Ornamentation is based on identified lithology while the unit codes are interpreted based on sequence of lithology. See Appendix V for mineral abbreviations and details of logging process. Stratigraphic unit codes are; Tngw = Waripi Limestone, Tngl = undifferentiated New Guinea Limestone Group limestone, Kkel = Ekmai Limestone, Kkes = Ekmai Sandstone. Dashed lines mark the upper and lower boundaries of unrecognised lithologies that are interpreted to represent fault zones. An asterisk is used to identify the location of the upper Waripi sandstone member, which is used to establish the total vertical offset.

LITHOLOGY LEGEND

-  Faumai Limestone
-  Waripi Limestone
-  Sandstone
-  Shale
-  Fault breccia
- * Upper Waripi marker

Figure 4-6 (cont.)

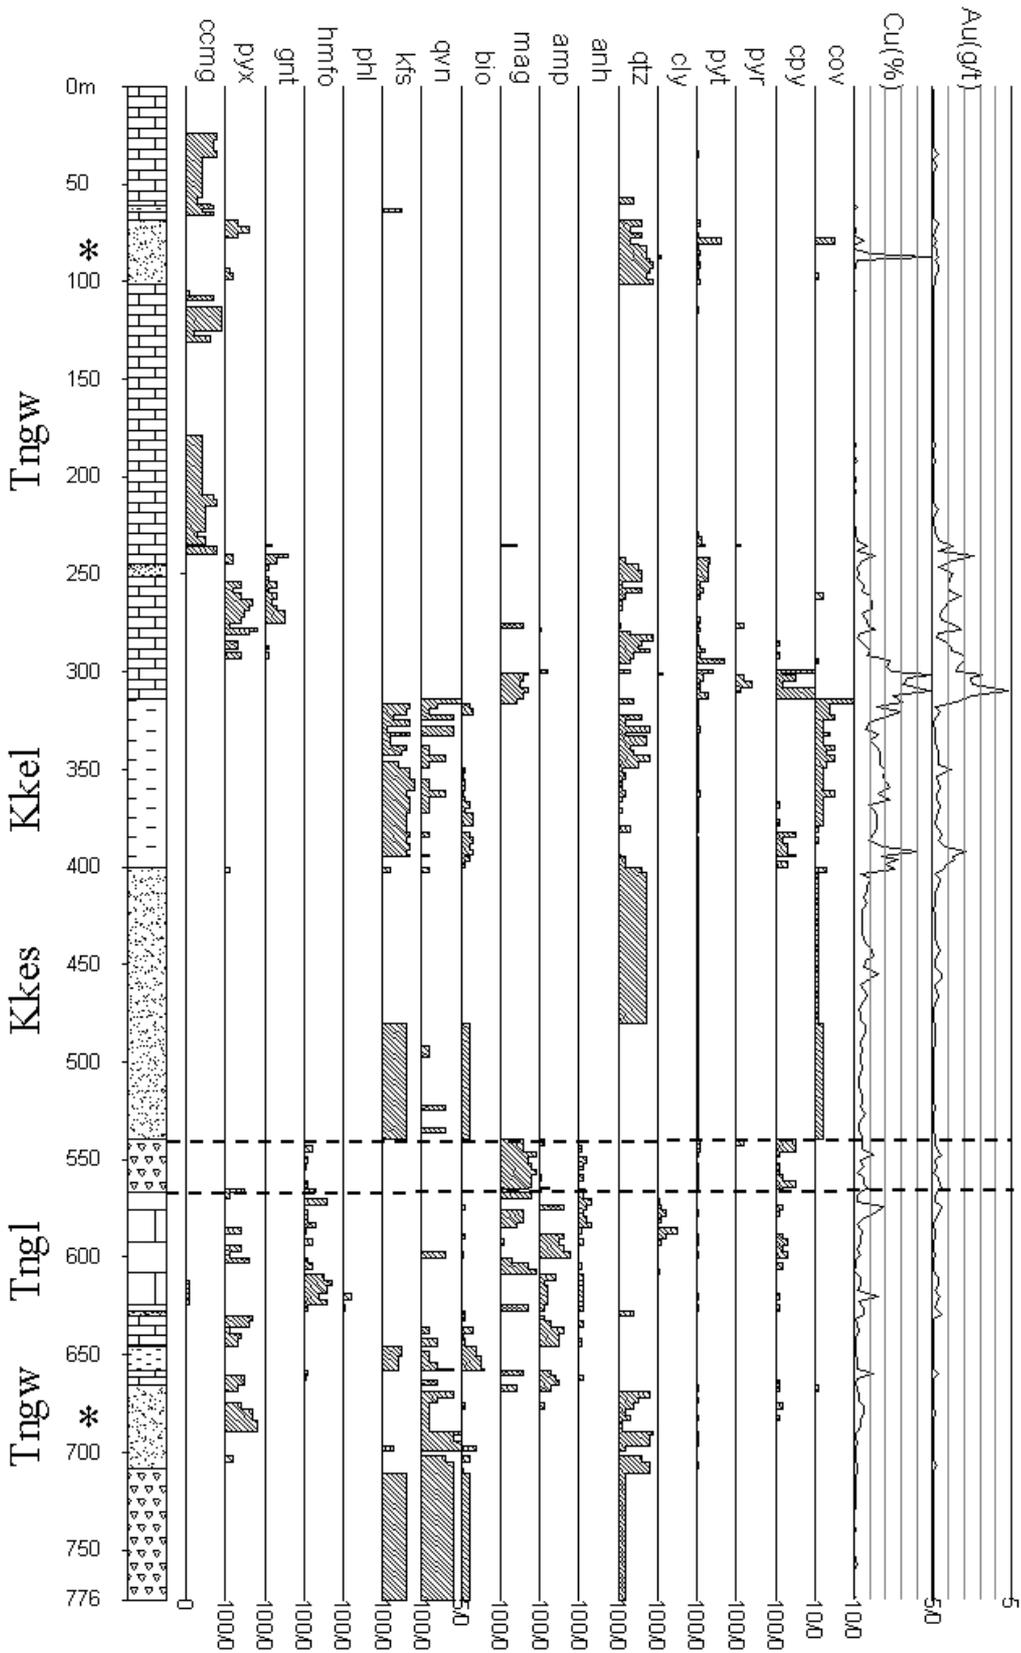

KL32-05 Simple faulted stratigraphic sequence

Figure 4-6 (cont.)



KL32-04 Complex fault and offset stratigraphy

Large-scale mineral distributions

Clinopyroxene \pm garnet skarn (see Chapter 3) is developed as thick (~20-50m-scale) lenses in the lower Waripi Limestone and Ekmai Limestone, parallel to the folded stratigraphy and are apparently truncated up dip by the Idenberg Fault Zone (Figure 4-7). Bodies with moderate to high preserved abundances of skarn-related minerals form a series of stacked lenses that occupy the lower Waripi and Ekmai Limestones, paralleling the bedding (Figure 4-7). Semi-concordant skarn rocks in the southeast of the deposit are concentrated in the lower Waripi Limestone and subordinate positions in the Ekmai Limestone (Figure 4-7). Skarn alteration does not persist to the northwest past the apparent truncation and thinning of the Ekmai Limestone (Figure 4-7). Early skarn is zoned with garnet occupying the primary channelways surrounded by clinopyroxene (*cf.* small-scale features illustrated in Section 3.2.1). Similarly, a large skarn body dominated by garnet occurs within the Idenberg Fault Zone. Skarn alteration maintains a constant thickness of 50m for 500m along strike, and maintains a constant position 50m above the base of the Waripi Limestone. The low density of data in these regions did not allow confident constructions of volumetric models for skarn mineral development in the footwall sequence to the southwest of the Idenberg Fault Zone.

Volumes of preserved moderate abundances of K-feldspar \pm biotite are tightly restricted to the Ekmai Limestone (Figure 4-8). In cross section, K-feldspar \pm biotite rocks are concentrated wholly within the Ekmai Limestone. Biotite alteration is most extensive where the Ekmai Limestone is thickest but is also concentrated in deeper portions of the Ekmai Sandstone and associated with the Idenberg Fault Zone (Figure 4-8). By contrast, moderately magnetite-rich rocks are prominent as a single concentration 20m thick along the base of the Waripi Limestone, extending along most of the identified strike extent (Figure 4-9). Significantly, the magnetite rocks extend into the Grasberg Igneous Complex where they appear to be portioned at the Grasberg Igneous Complex boundary, the first alteration to appear as such (Figure 4-9). At the deepest levels in the down-faulted stratigraphic package, magnetite is concentrated in limestone, assumed to be Faumai Limestone, above the upper Waripi sandstone member (Figure 4-9).

Retrograde skarn minerals tremolite-actinolite and serpentine have a similar distribution to magnetite, though details of any stratigraphical or structural control are not visible.

Quartz alteration is concentrated into stratigraphic layers abutting the Idenberg Fault Zone (Figure 4-10). Well-defined bodies of quartz-dominant material 10-50m thick were identified in drill core and are found to extend up to 500m along strike (Figure 4-10). Quartz alteration is less well developed in the east than in the west. Quartz alteration also occurs as a discrete package in the upper Waripi sandstone member. Moderate to high abundances of sulphides are concentrated within the Idenberg Fault Zone (i.e. broadly coincident with quartz alteration) (Figure 4-11). Additional smaller concentrations of sulphides are present along major stratigraphic contacts, particularly the Ekmai Limestone contacts. Sulphide concentrations are continuous for hundreds of metres along strike (Figure 4-11). Sulphide development is not continuous from the Idenberg Fault Zone to the Grasberg Igneous Complex. The independent development of chalcopyrite and covellite-bearing mineralisation is reconfirmed in models of their spatial distribution (Figure 4-11). Distributions of covellite-bearing mineralisation are distinctly concentrated about the Idenberg Fault Zone as well as in the adjacent Ekmai Limestone. In contrast, chalcopyrite-bearing mineralisation is concentrated along the Ekmai Limestone and is continuous into the Grasberg Igneous Complex.

Figure 4-7 Distribution of calcite, clinopyroxene, garnet, humite and phlogopite


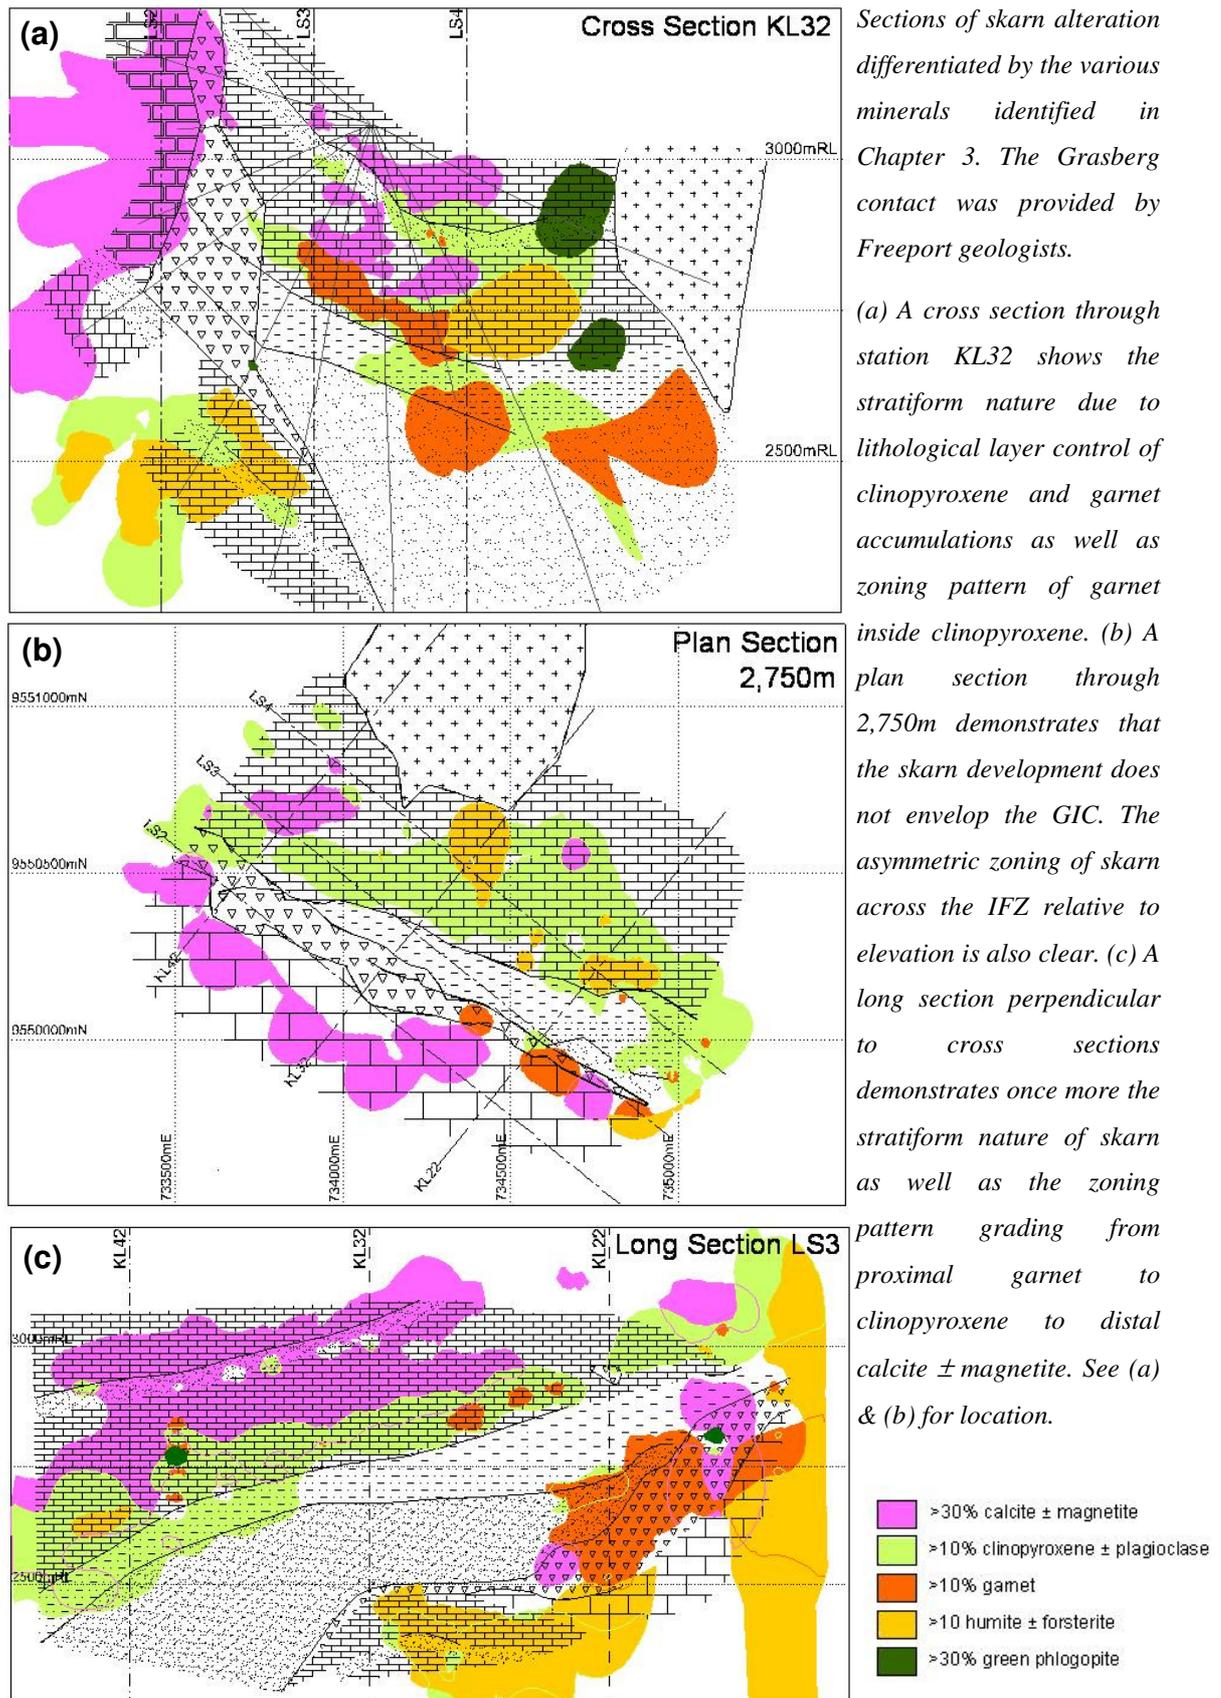


Figure 4-8 Distribution of dominant K-feldspar + biotite alteration

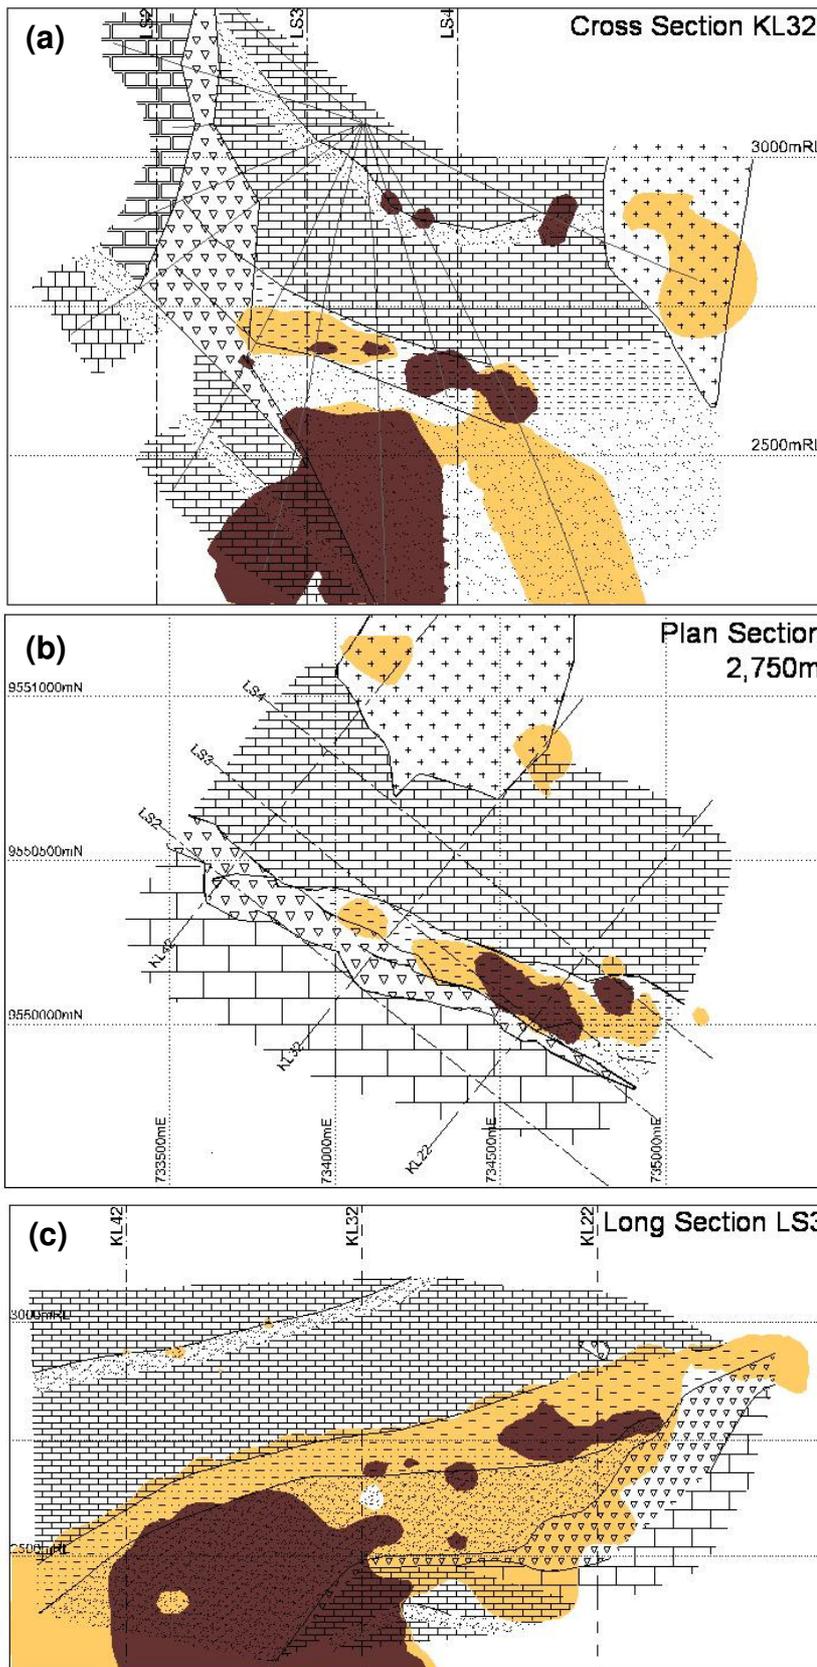


Sections of the distributions of the various potassic alteration group minerals identified in Chapter 3. The Grasberg contact was provided by Freeport geologists.

(a) A cross section through station KL32 shows the stratiform nature due to lithological layer control of K-feldspar and biotite accumulations. Deeper sections of Kucing Liar are biotite rich about the IFZ.

(b) A plan section through 2,750m demonstrates the lithological control as well as a suggestion of zoning from inboard biotite to more distal K-feldspar. (c) A long section perpendicular to cross sections demonstrates once more the lithological control highlighted in Chapter 3 as well as the zoning pattern grading from proximal biotite to more distal K-feldspar. See (a) & (b) for location.

(c) A long section perpendicular to cross sections demonstrates once more the lithological control highlighted in Chapter 3 as well as the zoning pattern grading from proximal biotite to more distal K-feldspar. See (a) & (b) for location.


Figure 4-9 Distribution of extensive magnetite and tremolite-actinolite alteration

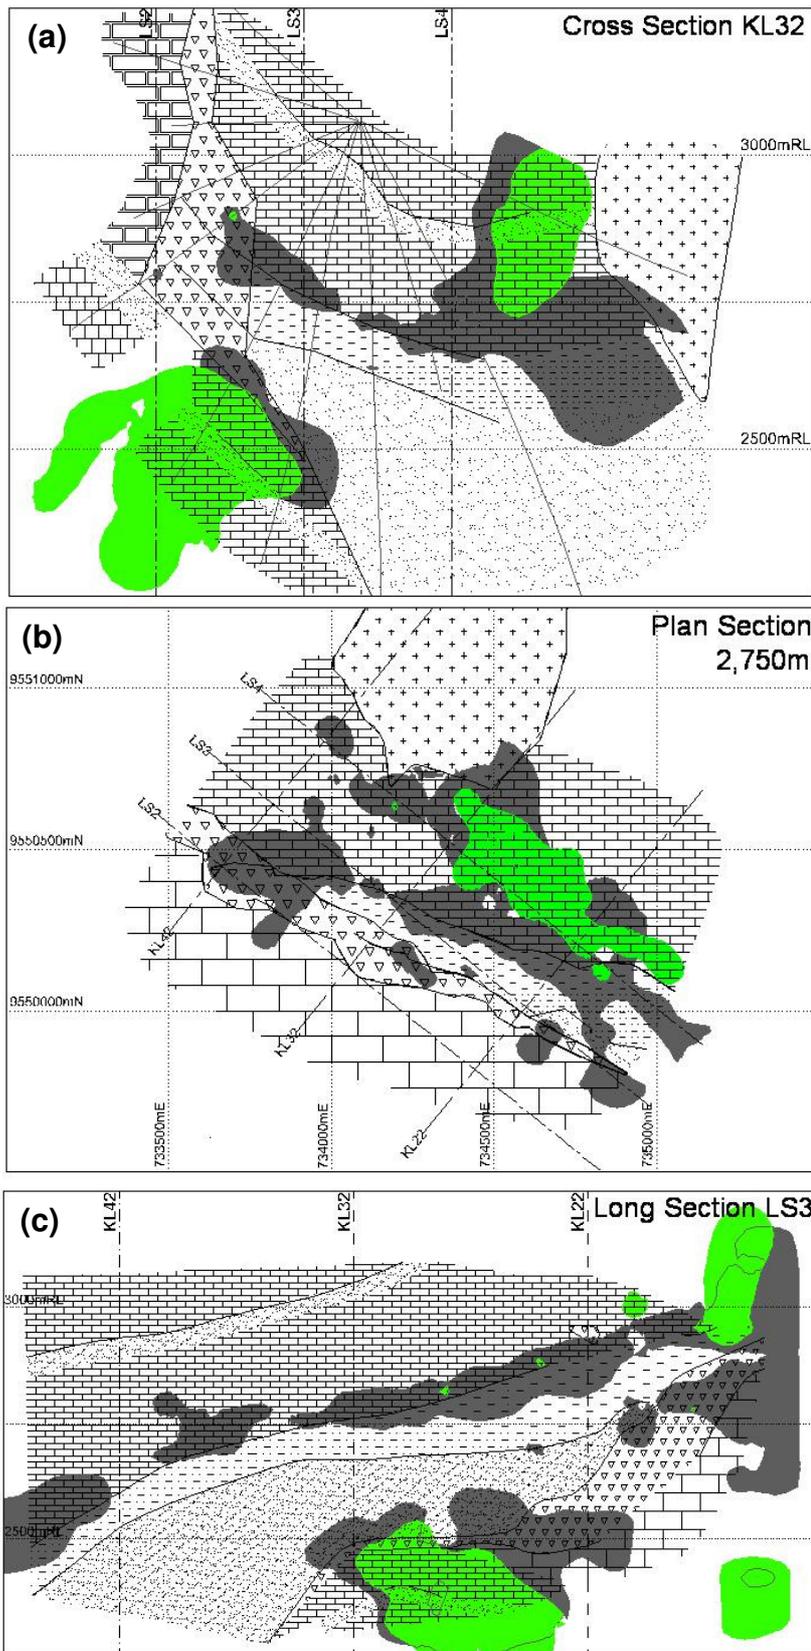

Sections of the distributions of magnetite and retrograde skarn alteration identified in Chapter 3 demonstrate the strong lithological (or stratigraphic contact) control on magnetite and retrograde skarn and also that retrograde skarn and some magnetite is not stratiform. The Grasberg contact was provided by Freeport geologists.

(a) A cross section through station KL32 shows that a large amount of magnetite is juxtaposed with the GIC. The section demonstrates a hydrothermal connection between the GIC and Kucing Liar during magnetite alteration (b) A plan section through 2,750m demonstrates the same connectivity with the GIC. (c) A long section perpendicular to cross-sections demonstrates once more the strong stratigraphical control. See (a) & (b) for location.


Figure 4-10 Distribution of rocks dominated by quartz, muscovite and anhydrite alteration

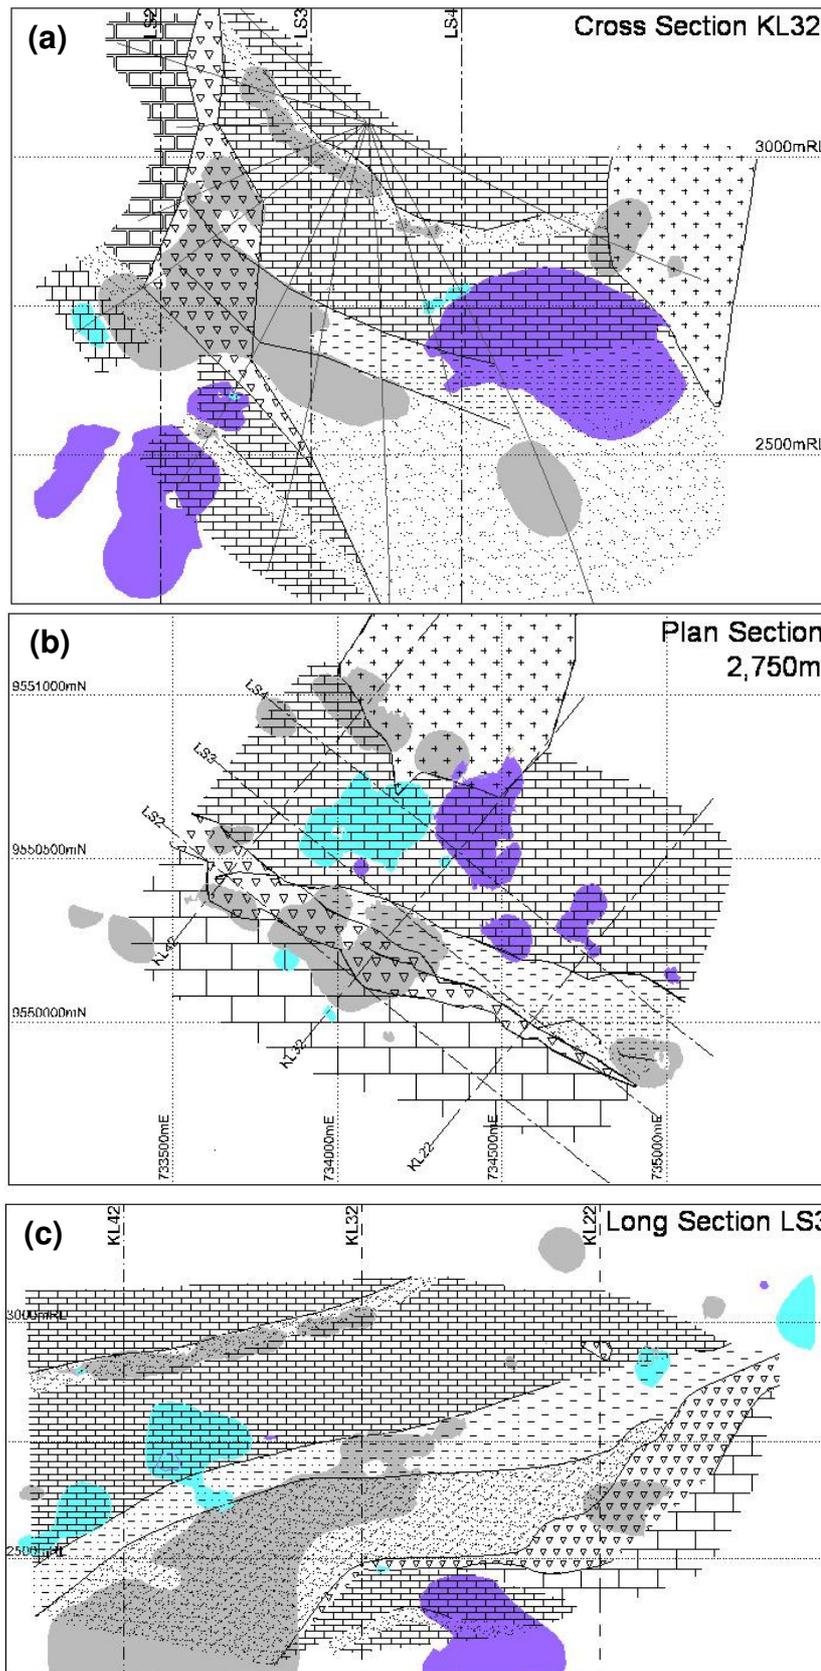

Sections of the distributions of quartz, anhydrite and talc-muscovite alteration identified in Chapter 3 demonstrate weak lithological control on quartz alteration but the disparate nature of this apparently temporally related assemblage.



(a) A cross section through station KL32 shows well the lithological control on quartz, where the stratigraphy is adjacent to the IFZ. The upper Waripi sandstone member has strongly partitioned some quartz alteration. Anhydrite distributions are very similar to that of tremolite-actinolite but show no clear structural control. (b) A plan section through 2,750m suggests a parallel structure at the margin of GIC has concentrated quartz alteration. (c) A long section perpendicular to cross sections demonstrates once more the strong stratigraphical control. See (a) & (b) for location.

Figure 4-11 Distribution of ore sulphides, pyrite, chalcopyrite and covellite

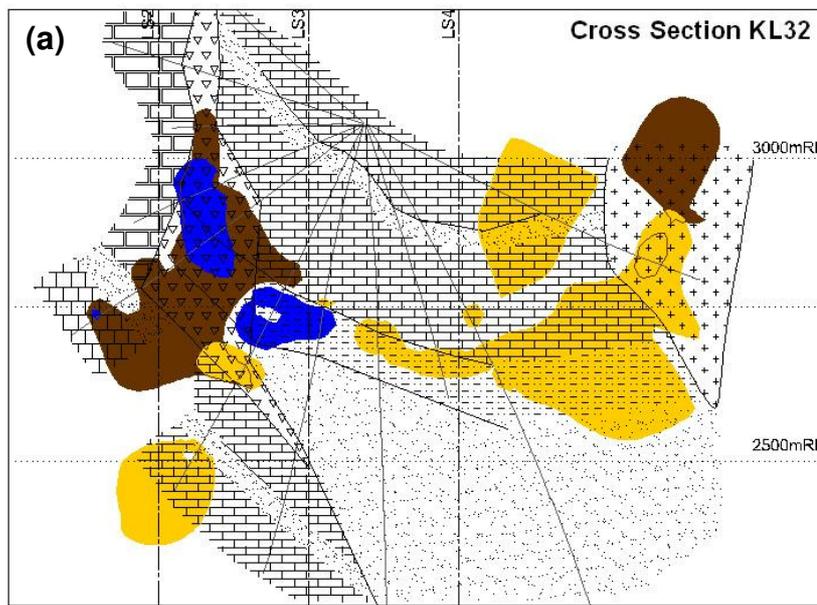


Sections of the distributions of pyrite, chalcopyrite and covellite demonstrate the strong influence of the IFZ and more subtle lithological control on ore minerals as well as a zoning pattern about the IFZ of proximal covellite and distal chalcopyrite.

(a) A cross section through station KL32 shows the intensity of pyrite and covellite development in the IFZ offset as well as the influence of the Ekmai Limestone. (b) A plan section through 2,750m shows the most intense pyrite alteration is opposite the GIC. Note that the contact zone of Kucing Liar and the GIC where magnetite and retrograde skarn are concentrated is occupied by high chalcopyrite concentrations.

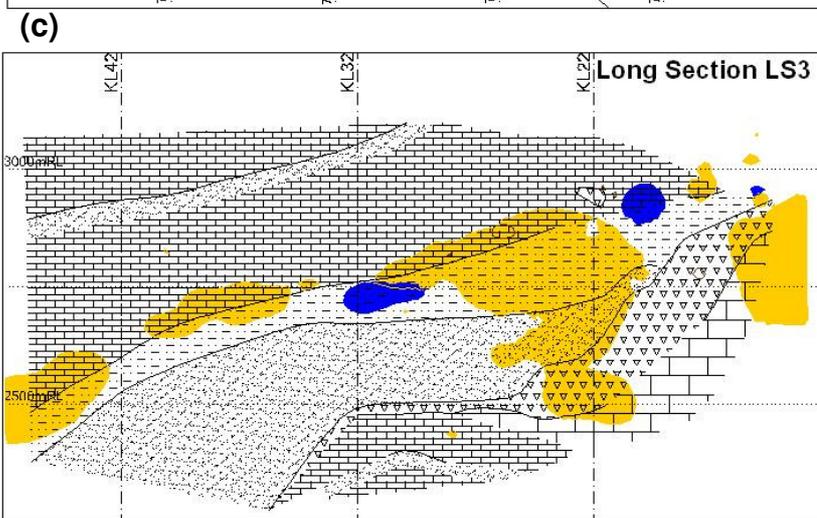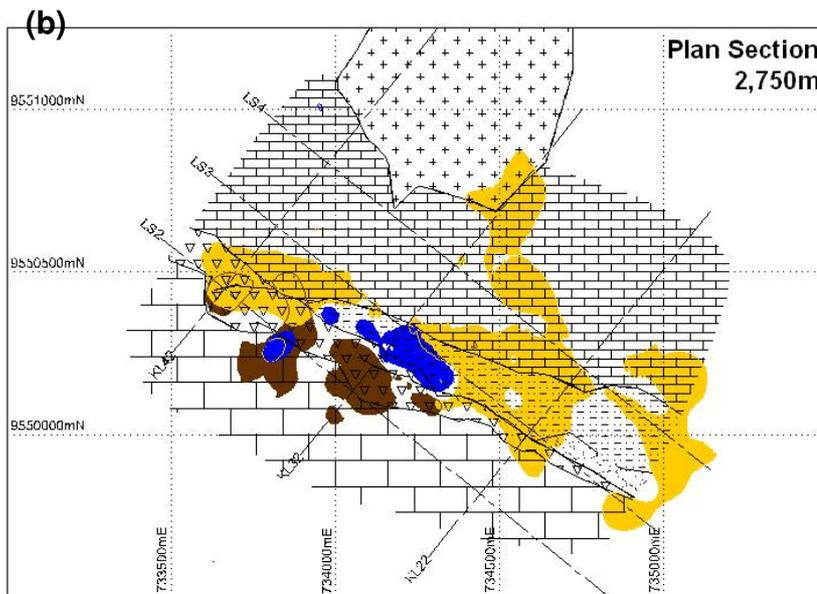

(c) A long section perpendicular to cross sections further demonstrates the zoning pattern of ore minerals. See (a) & (b) for location.



4.2 LARGE-SCALE CONTROLS ON FLUID INFILTRATION

The data in this chapter will show that the Kucing Liar hydrothermal system was related to a major structural offset in the Idenberg Fault Zone, which is adjacent to a significant lithological contrast.

4.2.1 Structural geometry of Kucing Liar alteration

The combination of specific rock types and marker horizons (Chapter 2) has enabled construction of a lithological model for the mineralised zone. Models of these data indicate that Kucing Liar lies within the north dipping limb of a syncline, although no fold closures are evident in the study area. Adjacent to the Grasberg Igneous Complex the bedding is folded against the intrusion contact, suggesting forceful intrusion. The host stratigraphy has been truncated at a very shallow angle to strike by a steeply dipping fault zone. The fault zone is named the Idenberg Fault Zone and contains several steeply northeast dipping narrow structures that are connected by wide zones of brecciation. The zone of displacement follows both the narrow structures and wide zones to produce a series of offsets within the fault zone. The displaced portion of Kucing Liar on the southwest of the Idenberg Fault Zone is difficult to analyse due to very low data densities. The same rock types are encountered in the footwall of the Idenberg Fault Zone, though skarn is more prevalent than other alteration types.

The mineral distribution data indicate the Idenberg Fault Zone focussed the entire system while a series of complex offsets in the fault zone provided local controls, specifically on garnet and sulphide distributions. Specific alteration assemblages are concentrated along the lower Waripi and Ekmai Limestone contacts, as well as within the Idenberg Fault Zone, especially within offsets of the fault. Within the mineralised zone hydrothermal alteration occupies the upper sandstone member of the Waripi Limestone, the lower Waripi Limestone, the Ekmai Limestone and also extends downwards into the Ekmai Sandstone. Skarn alteration tends to be stratiform and is concentrated in the Ekmai Limestone and lower half of the Waripi Limestone. Humite-forsterite

± serpentine and clinopyroxene ± tremolite-actinolite are restricted to the dolomitic Waripi Limestone (see Chapter 2) within the main mineralised zone and appear to stratiform and interlayered, perhaps reflecting the original distribution of dolomite and calcite in the limestone unit. Garnet and magnetite are localised within the Waripi Limestone along its lower contact with the Ekmai Limestone and to a lesser extent along the base of the Ekmai Limestone. Small concentrations of garnet are also localised along the upper skarn contact within the Waripi Limestone. K-feldspar ± biotite, along with related quartz veins, is generally restricted to the Ekmai Limestone and Ekmai Sandstone though biotite also formed independently within narrow portions of the Idenberg Fault Zone below the elevation of the main mineralised zone. Quartz and sulphide alteration have very similar distributions that appear to parallel the steeply dipping structures within the Idenberg Fault Zone and are concentrated about a large-scale offset in the fault zone. Quartz and sulphide are structurally distinct from other alteration assemblage, as they do not form large stratiform bodies. The change in alteration distribution from skarn to potassic to silica-pyrite indicates a change in structural controls that will be analysed in the next section. The relationship between chalcopyrite and covellite mineralisation in Kucing Liar and the Grasberg porphyry system has not been comprehensively tested, though the two systems have similar ore assemblages, there are some grounds for believing the two are distinct systems, and will be further discussed in Chapter 9.

The data indicate mineralisation that is zoned with respect to fluid flow. Mertig *et al.*, (1994), Hefton *et al.*, (1995), and Rubin and Kyle (1998) have described vertical zonation of alteration and mineralisation in the magnesian skarn deposits of the EESS, formally referred to as GBT-IOZ-DOZ (see Chapter 1). The focus of fluid flow at Kucing Liar was the Idenberg Fault Zone, and in particular offset within it, and fluids probably flowed upwards and along stratigraphic contacts to that feature. Fluids may then have migrated within the Idenberg Fault Zone to higher elevations. In a model where covellite formation is at least partly contemporaneous with, though spatially distinct from, chalcopyrite, the data suggest that chalcopyrite ± pyrite was accompanied by and locally overprinted by covellite ± pyrite, which is restricted to the high flow areas. Both of

these forms of copper mineralisation were replaced in the core of the Idenberg Fault Zone by a package of pyrite \pm chalcopyrite \pm covellite. Pyrite, chalcopyrite and covellite core are overprinted by galena and sphalerite.

4.2.2 Driving forces of fluid flow

Fluid infiltration through rocks may be via primary or secondary porosity. Primary porosity is a function of the grain size, degree of cementation and distribution of the wall rocks, while secondary porosity is that which is created during deformation or alteration in the absence of deformation. The very fine-grained texture of rock samples, particularly pyroxene and feldspar, indicate derivation from rapid deposition at numerous nucleation sites, which can result from high fluid fluxes that are conducive to supersaturation (Einaudi *et al.*, 1981). Additionally, pervasive fluid flow such as is observed to have occurred during skarn and potassic (K-feldspar \pm biotite) alteration is inferred to occur along microcracks and grain-boundary porosity (Oliver, 1996). Pervasive fluid flow produces uniform replacement of wall rocks, referred to as penetrative alteration (Chapter 3). Widespread penetrative alteration is indicative of low fluid pressures and will typically be associated with relatively high fluid fluxes as compared to channelled flow (Oliver, 1996). Channelled fluid flow occurs along fractures in wall rocks but is accompanied by substantial infiltration into the local wall rocks, typically resulting in a mineralogical selvedge (Oliver, 1996). The progressively declining scales of penetrative alteration accompanied by increased fracture selvedge and infill indicate that fluid flow became more and more channelled accompanied by increasing fluid pressures. There are also indications that the amount of channelled fluid flow increased with time, evidenced by the increase in infill relative to alteration and the decrease in penetrative alteration in later stages of the paragenesis (Chapter 3).

Within a fault zone, fluid migration occurs from zones of high interstitial pressure and high strain (contraction zone) to zones of low interstitial pressure (dilation zone) (Guha *et al.*, 1983). Flow localization within faults and shear zones occurs in areas of highest fracture aperture and fracture density, such as damage zones associated with fault jogs, bends and splays (Cox *et al.*, 2001).

Offsets are thus favourable sites for fluid flow due to complex geometry created by the large amount of wall rock partings and intersections of variably oriented fractures. Fluid flow in a fault network is governed by creation of permeability through movement. Where high fluid pressures produce low effective confining pressures, grain scale crack growth significantly increases the permeability of the active shear zone relative to their host rocks (Cox *et al.*, 2001). Thus, secondary permeability is created by high pore fluid pressure regimes, which favour fracture growth (Cox *et al.*, 2001). Mineral-filled fractures in hydrothermal systems indicate tensile effective stress states, and thus, fluid pressures greater than σ_3 (lithostatic load) (Cox *et al.*, 2001). Sustained hydrothermal flow must be accompanied by repetitive and continued wall rock fracturing given that mineral sealing is rapid compared to the lifetimes of hydrothermal systems (Cox *et al.*, 2001). Consequently, sustained fluid flow occurs only in active structures where permeability is repeatedly renewed. Fault motion is accommodated by earthquake-related rupturing (Sibson, 2001) and is accompanied by significant fluid redistribution that occurs throughout the aftershock phase following large earthquakes (Cox *et al.*, 2001). Secondary porosity related to lithological layering may also be produced during folding as deformation of heterogeneous rocks creates dilatancy due to competency contrast, as well as large variations in pore fluid pressure (P_f), leading to brecciation along these contacts (Oliver *et al.*, 2001).

Thus deformation can explain brecciation along the base of the Waripi Limestone. In similar fashion to Kucing Liar, the Big Gossan deposit is concentrated in breccia bodies within the lower Waripi Limestone near the contact with the Ekmai Limestone, which was altered to pyroxene-feldspar and biotite-feldspar hornfels and also contains local garnet-pyroxene skarn (Meinert *et al.*, 1997). The preference for the Ekmai Limestone as a host for quartz vein arrays may also be derived from ground preparation due to contact metamorphism of the shaly limestone, as brittle calc-hornfels are easily fractured during deformation (Einaudi *et al.*, 1981).

5 Ore mineral distribution and metal zoning

Chapter 2 identified two primary forms of copper mineralisation; one dominated by chalcopyrite associated with skarn and magnetite-tremolite alteration and a second dominated by covellite associated with extensive quartz alteration accompanying leaching and muscovite-talc alteration of skarn and aluminosilicate rocks. While other copper-bearing minerals, namely enargite, bornite, nukundamite, digenite and chalcocite were identified, they do not occur in quantities that could be recorded alongside chalcopyrite and covellite. In addition to copper, visible molybdenite was also identified. No visible gold or gold-bearing minerals were identified, although assay data indicate that gold, as well as other trace metals are also enriched to varying degrees. PT Freeport Indonesia has established that the quantities of copper and gold contained within Kucing Liar are economically significant (see Chapter 1). The aim of this chapter is to determine the characteristics of copper and gold mineralisation in Kucing Liar with the goal of establishing the primary controls on ore deposition. The methods followed to completely portray the distribution of mineralisation are:

1. Graphical analysis of the relationships between minerals and metals
2. Modelling the spatial distribution of copper, gold and trace metals

A 13 metal assay suite was made available by Freeport Indonesia and these samples correlate with mineralogical-lithological logging data (Appendix V). Three-dimensional contours of the metal assays were constructed and are presented here in sections. The quantitative mineral database introduced in Chapter 4 is used here to constrain the metal analyses in terms of alteration and mineralisation assemblages. From these data the primary characteristics of Kucing Liar mineralisation, including the number of mineralising episodes and their metallogenic signatures can be determined.

5.1 MINERALISATION POPULATIONS AND SPATIAL DISTRIBUTIONS

The results are grouped into two sections which document firstly the large-scale distributions of mineral and metal relationships are analysed in relation to the structural setting determined in Chapter 4 followed by a more detailed examination of the data by reviewing the relationships between metals within distinct mineral associations.

5.1.1 Spatial models of ore mineral and metal distributions

Spatial models include downhole correlations, 3-dimensional wireframe objects as well as average abundances within elevation ranges in order to determine the large-scale zoning patterns of Kucing Liar. Three-dimensional models of metal distribution have been developed using Leapfrog™ (Zaparo) software, which generates iso-surfaces for a specific grade range(s) of a variable to develop a 3D contour. A selection of grade ranges has been selected for each metal. The critical sections presented here are derived from 3-dimensional wireframes that cover the entire mineralised zone and thus represent all data rather than data projected locally on the individual section planes.

Metal distributions relative to the structural setting

Local controls on mineralisation are illustrated by the nature of element dispersion pattern about the primary recognisable structures such as the Idenberg Fault Zone and the major lithostratigraphic contacts. Copper and gold occur in narrow high-grade zones within broader zones of low-level metal concentrations (Figure 5-1). Broad zones of greater than 1% Cu and 1g/t Au extend for 100-300m within single drill holes, including short sections (5-10m) of much higher grades up to 5% Cu and 5g/t Au (Figure 5-1b and c). The upper limit of mineralisation is in the middle of the Waripi limestone and is generally an abrupt transition from zero metal content, where a sandstone layer has been recognised in the sequence (see Chapter 2), while the lower boundary of copper-gold mineralisation is gradational over hundreds of metres. High-grade intervals (>2%Cu and/or >2g/tAu) up to 25m wide occur locally in these broad low-grade zones.


Grade distributions are commonly symmetrical though an example of systematic grade increase within the Idenberg Fault Zone is present in KL32-04 from 250-300m (Figure 5-1c).

In general, the higher copper and gold grades are coincident although there is some separation at finer scale (Figure 5-1). Lithological control on copper-gold mineralisation is demonstrated by high grades associated with the upper and lower contacts of the Ekmai limestone (Figure 5-1b). Intersections of undisturbed stratigraphy as illustrated in KL32-05 reveal narrow zones (5-10m) of high-grades concentrated at the Ekmai limestone contact surrounded by gradually decreasing lower grades. A discrete zone of mineralisation, recognised in core samples, is often present within the upper Waripi sandstone member (see KL32-05, Figure 5-1b). The very close association of high copper and gold grades and the position of the Idenberg Fault Zone demonstrate the primary control of this feature on mineralisation. Deeper intersections of the Idenberg Fault Zone, as illustrated in KL32-05, are not significantly mineralised. Copper-gold enrichment is generally symmetrical about the position of the controlling feature, though an example of asymmetric copper and gold distribution occurs in the interval from 250-300m in KL32-04 where grade progressively increases with depth at the interpreted position of the Waripi-Ekmai limestone contact (Figure 5-1c).

Sphalerite and galena are concentrated in zones directly above the main mineralised zone predominantly within unaltered Waripi limestone. Silver is closely associated with the lead and zinc enrichment. At around ~275m depth in KL32-01 (Figure 5-1a), Ag, Zn and Pb occur as a halo about the Idenberg Fault Zone where they are also associated with elevated gold that is not directly related to copper mineralisation. Ag, Zn and Pb also occur in the main orebody but their distribution is erratic. Cu, Au, Ag, Zn and Pb grades correlate closely in the Idenberg Fault Zone in a section of KL32-04 beginning at 450m, although a different association of Cu, Au, Ag, Co and Se without Zn or Pb is also present from 475m in the same structural zone (Figure 5-1c).

Figure 5-1 Downhole distribution of metal concentrations

Three structural settings are used to illustrate copper-gold enrichment patterns, including an intersection of the Idenberg Fault Zone within the upper Waripi limestone (a), an example of an intersection of relatively undisturbed stratigraphy truncated at depth by a narrow fault zone (b), and finally a complicated section of the Idenberg Fault Zone involving truncation of the Ekmai limestone (c). Dashed lines mark the upper and lower boundaries of unrecognised lithologies that are interpreted to represent fault zones. An asterisk is used to identify the location of the upper Waripi sandstone member, which is used to establish the total vertical offset. Ellipses are drawn around specific metal associations which are referred to in the text.

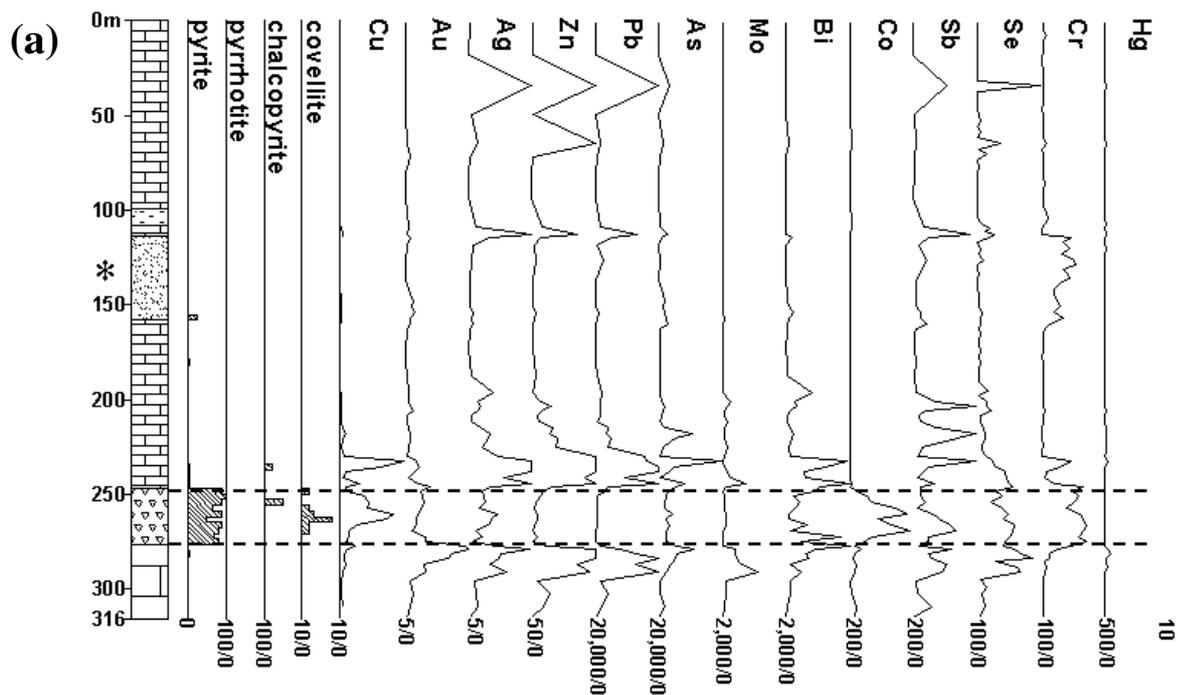


KL32-01 Idenberg Fault in relatively unaltered hosts

LITHOLOGY LEGEND


-  Faumai Limestone
-  Waripi Limestone
-  Sandstone
-  Shale
-  Fault breccia
-  Upper Waripi marker

Figure 5-1 cont.

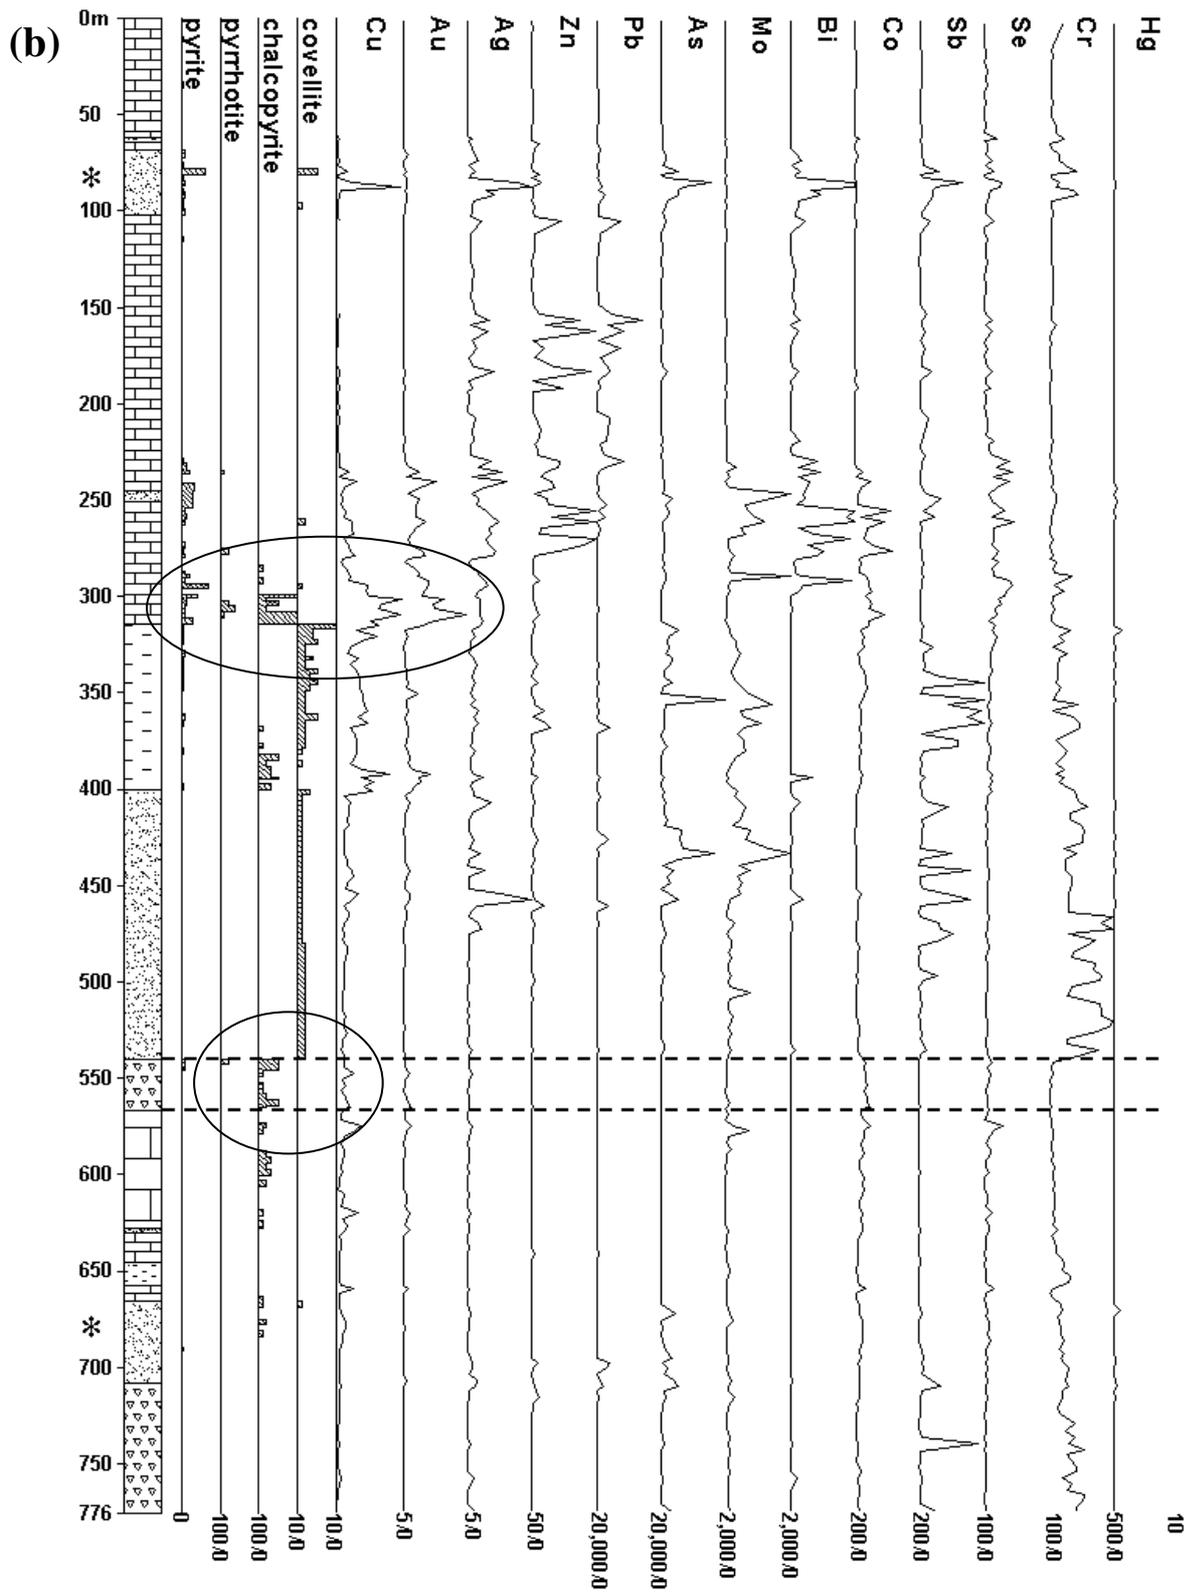

KL32-05 Simple faulted stratigraphic sequence

Figure 5-1 cont.

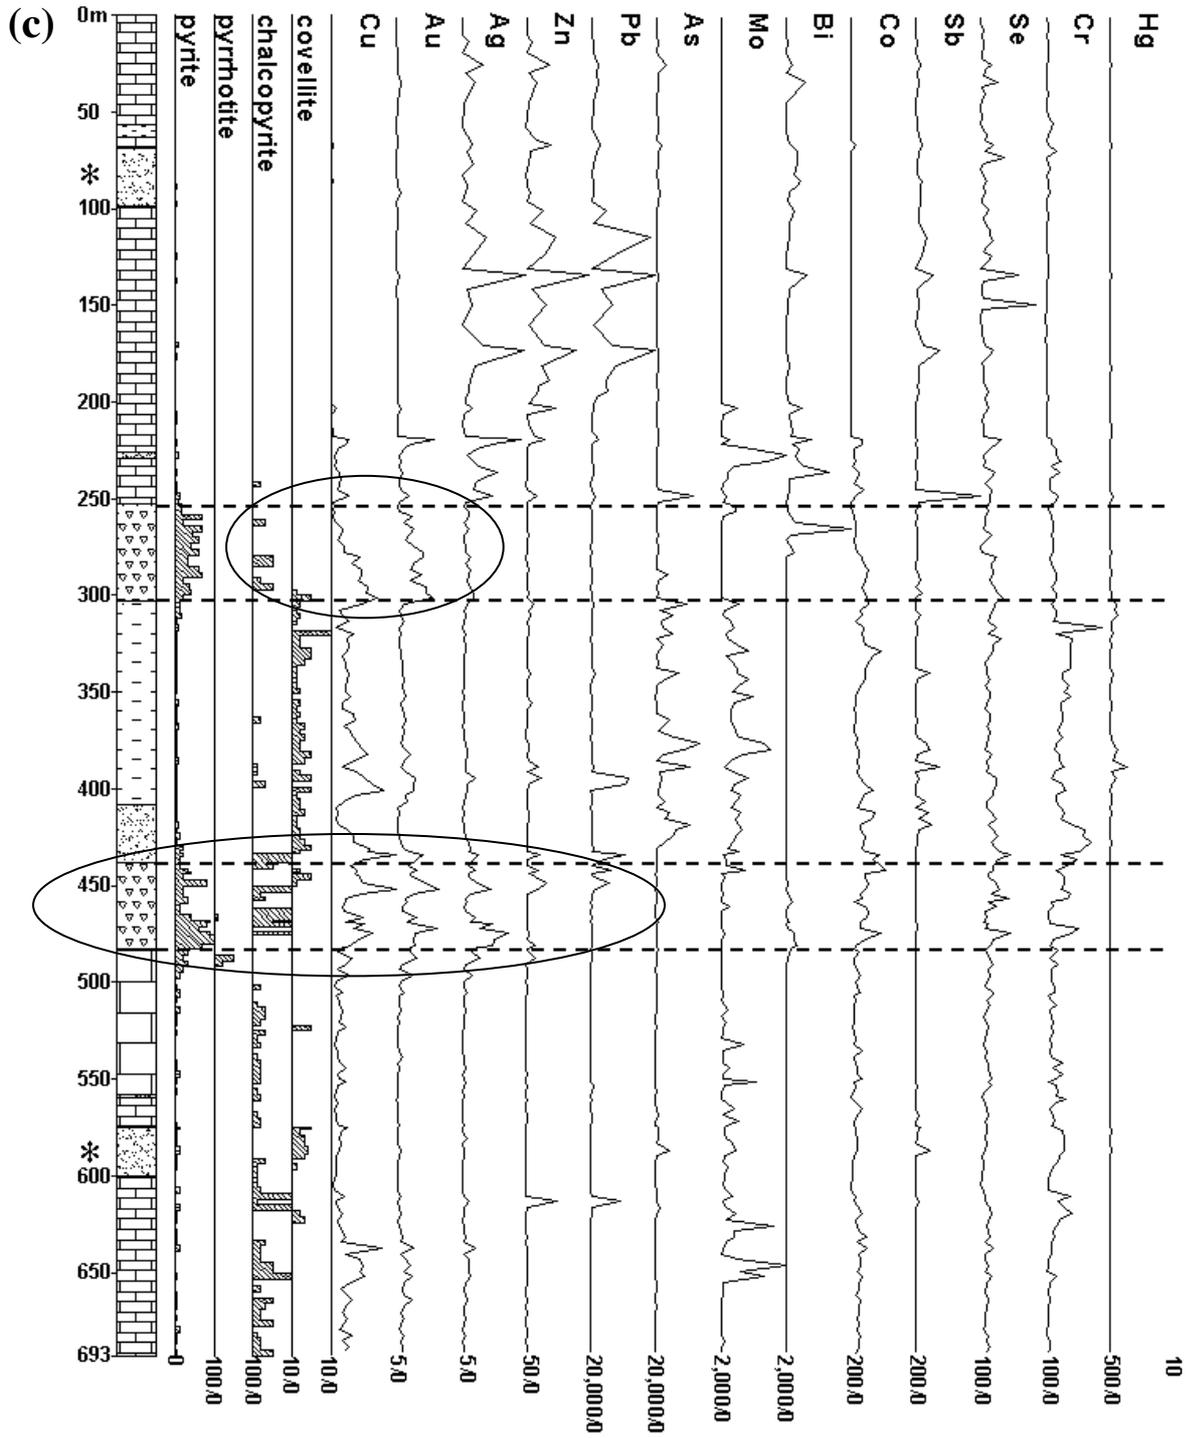


KL32-04 Complex fault and offset stratigraphy

Large-scale patterns of ore mineral and metal enrichment

The ore minerals pyrite, chalcopyrite and covellite are the only sulphides modelled, as they exist in high enough concentrations to enable data continuity between cross sections. These models indicate that pyrite is strongly restricted to the primary offset in the Idenberg Fault Zone and the Ekmai Limestone contact where it is adjacent (Figure 5-2). The distribution of chalcopyrite indicates strong partitioning along the upper Ekmai Limestone contact as well as a distinct connection between mineralisation in Kucing Liar and the Grasberg Igneous Complex (Figure 5-3). Meanwhile, covellite is strongly partitioned into the Idenberg Fault Zone offset as well as the main body of the Ekmai Limestone (Figure 5-4). The distribution of ore sulphides points to a zoning pattern of covellite-chalcopyrite centred on the Idenberg Fault Zone.


Spatial models of metal grade ranges show that metals are concentrated into major structural features, in particular the zone of offset within the Idenberg Fault Zone (IFZ) and along the lower Waripi limestone and upper and lower contacts of the Ekmai limestone where these are adjacent to the fault (Figure 5-5 to Figure 5-11). Grade patterns are symmetrical about central highly mineralised zones and there are no apparent truncations of grade continuity. Contacts between the Ekmai Limestone (Kkel) and Waripi Limestone (Tngw) adjacent to the Idenberg Fault Zone were the major conduits for metal-bearing solutions. Mineralisation is characterised by a core of copper and gold, which is surrounded by a composite halo of proximal silver and distal zinc-lead. Ag-Zn-Pb mineralisation in the halo is most concentrated at the hinge mark, which is coincident with the Idenberg Fault Zone, where there is also concentrated gold, arsenic and antimony.

Figure 5-2 Spatial distribution and structural controls of pyrite alteration

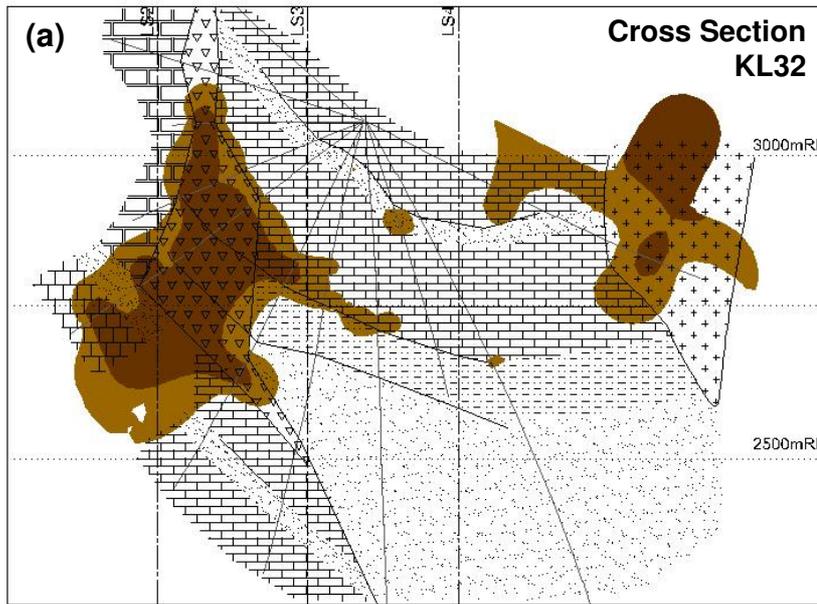


Sections of the distributions of pyrite demonstrate the strong influence of the IFZ and the adjacent Ekmai Limestone (Kkel) contact. It also indicates that intense pyrite alteration occurs within the GIC at the same elevation as Kucing Liar.

(a) A cross section through station KL32 shows intensity of pyrite in the IFZ offset as well as the extensions along the Kkel and low IFZ contacts.

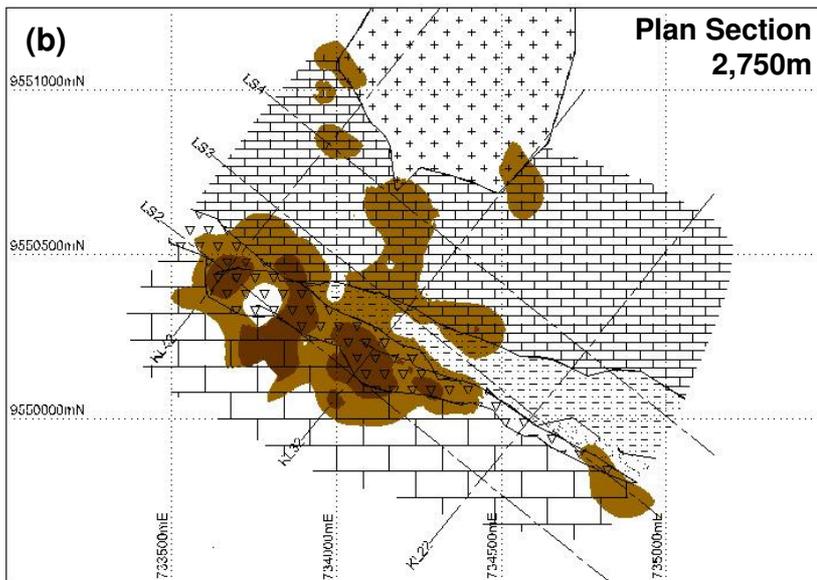

(b) A plan section through 2,750m shows the most intense pyrite alteration is opposite the GIC. The section shows that pyrite is not laterally continuous across the deposit.

(c) A long section perpendicular to cross sections demonstrates that pyrite does extend along strike within the low Waripi Limestone where it is adjacent to the IFZ.

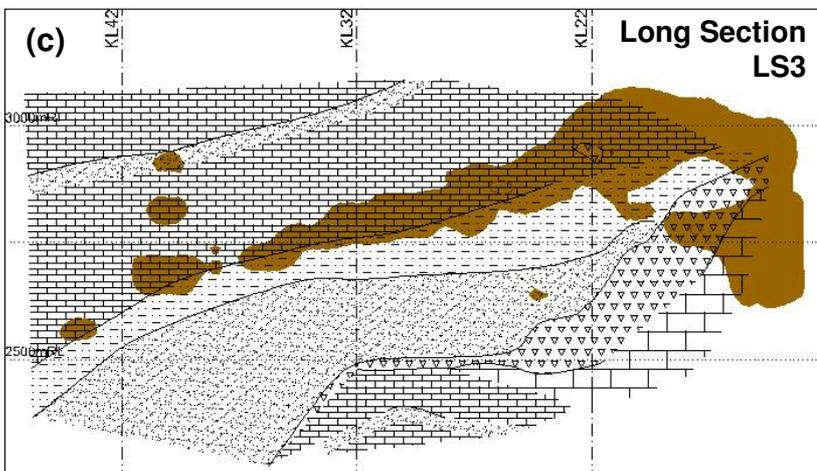

The intensity of pyrite within stratigraphic layering will be dependent on the distance from the IFZ. See (a) & (b) for location.

>5% pyrite
 >10% pyrite

Figure 5-3 Spatial distribution and structural controls of chalcopyrite



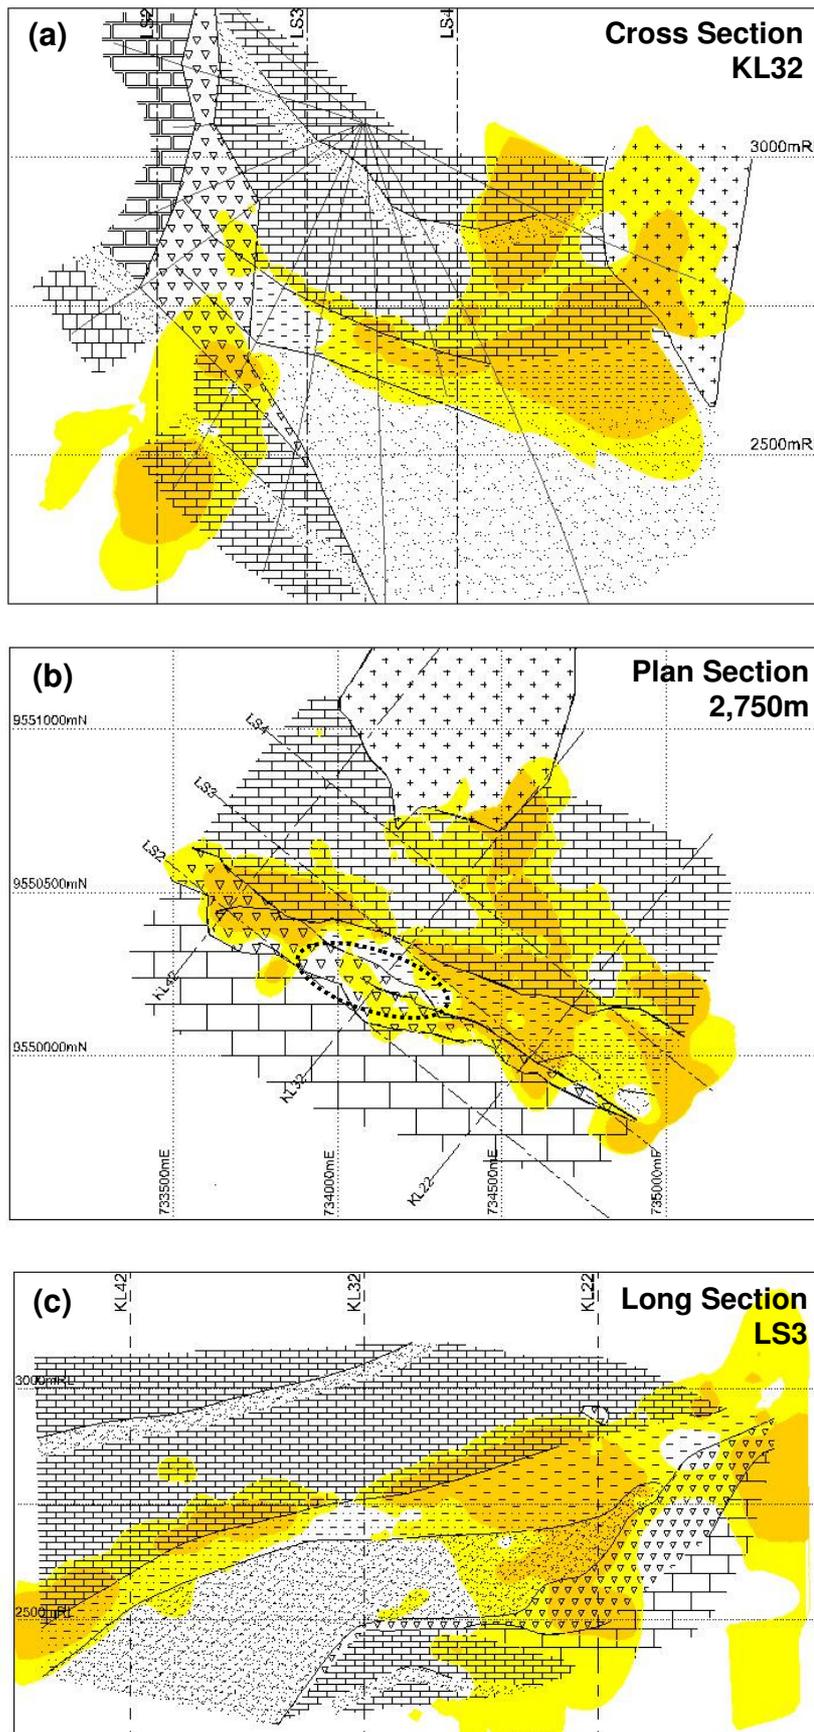



Figure 5-4 Spatial distribution and structural controls of covellite

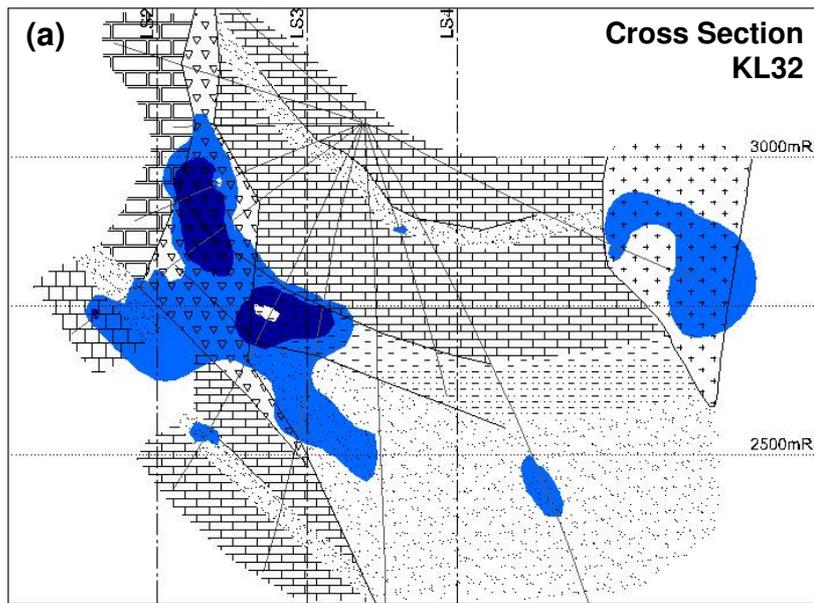

Sections of covellite concentration models overlain on drilling traces and the lithological model described in Chapter 2. The Grasberg contact was provided by Freeport geologists. Ornamentation is same as lithological models in Chapter 4. (a) A cross section through station KL32 indicates two zones of intense covellite mineralisation within the IFZ offset and within the Kkel adjacent to the IFZ.

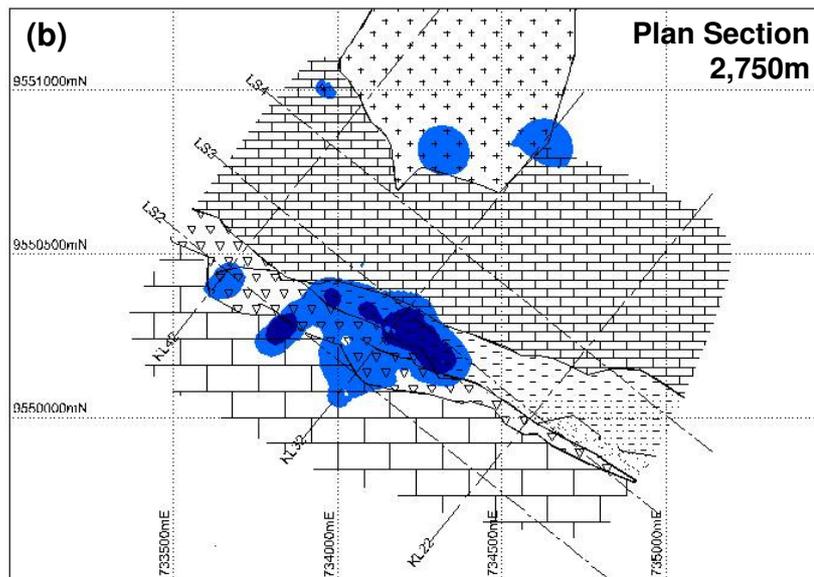


Low intensity covellite mineralisation occurs in the footwall of the IFZ along layering in the vicinity of sandstone. Note a zone of weak covellite mineralisation occurs within the GIC. (b) A plan section through 2,750m shows that covellite is also restricted along strike and appears as a core to the chalcopyrite distributions in Figure 5-3.

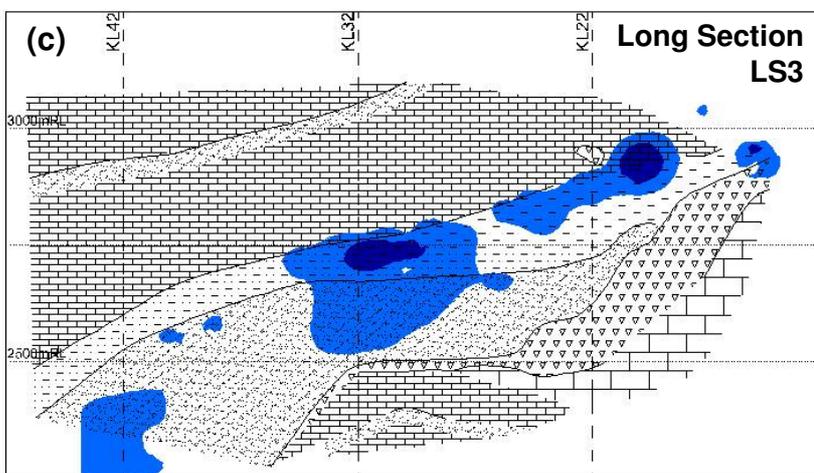

(c) A long section perpendicular to cross sections reinforces the concept of covellite occupying a core position relative to chalcopyrite. See (a) & (b) for location.


>1% covellite
 >2% covellite

Figure 5-5 Spatial distribution and structural controls of copper

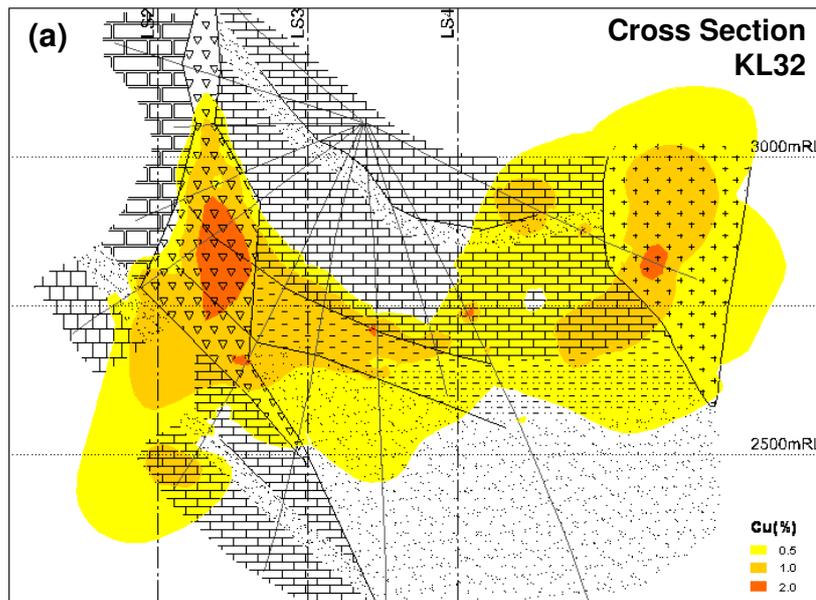


Sections of copper concentration models overlain on drilling traces and the lithological model described in Chapter 4. The Grasberg contact was provided by Freeport geologists

(a) A cross section through station KL32. The concentration of copper in the Idenberg Fault Zone and Ekmai limestone is clear. The models indicate some overlap of Cu grade between Kucing Liar and the GIC. Data is scarce in the GIC and contours of Cu-concentration in that area are poorly constrained.

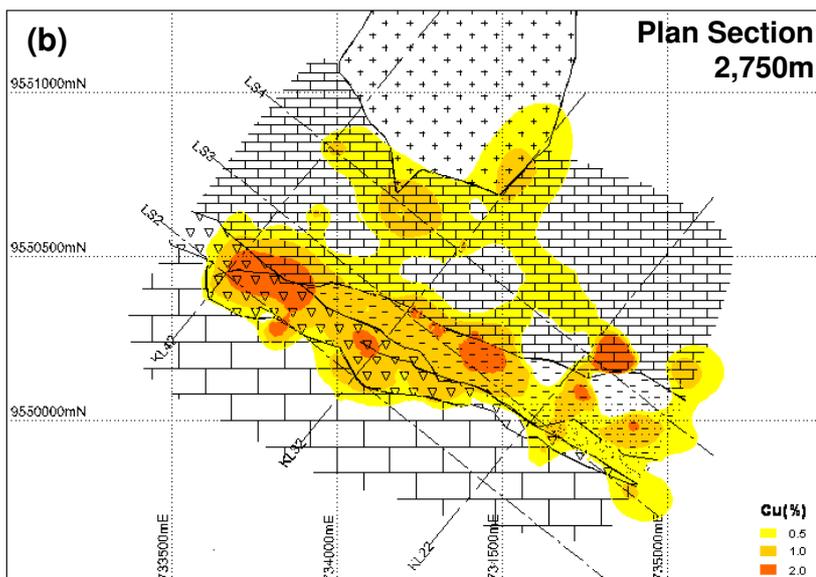


(b) A plan section through 2,750m indicates Kucing Liar Cu-mineralisation sits in the IFZ directly across from the GIC, which has a separate grade annulus about it.

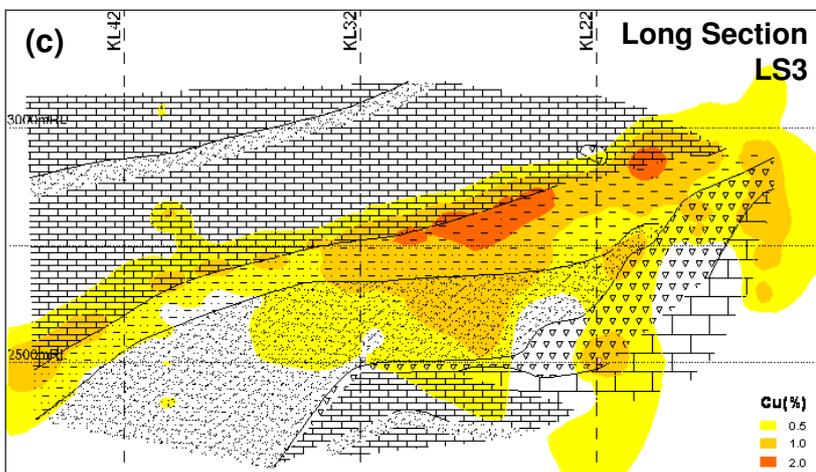


(c) A long section perpendicular to cross sections shows the strong control on Cu-grade by the Kkel-Tngw contact as well as the lateral extent of mineralisation. See (a) & (b) for location.

Figure 5-6 Spatial distribution and structural controls of zinc

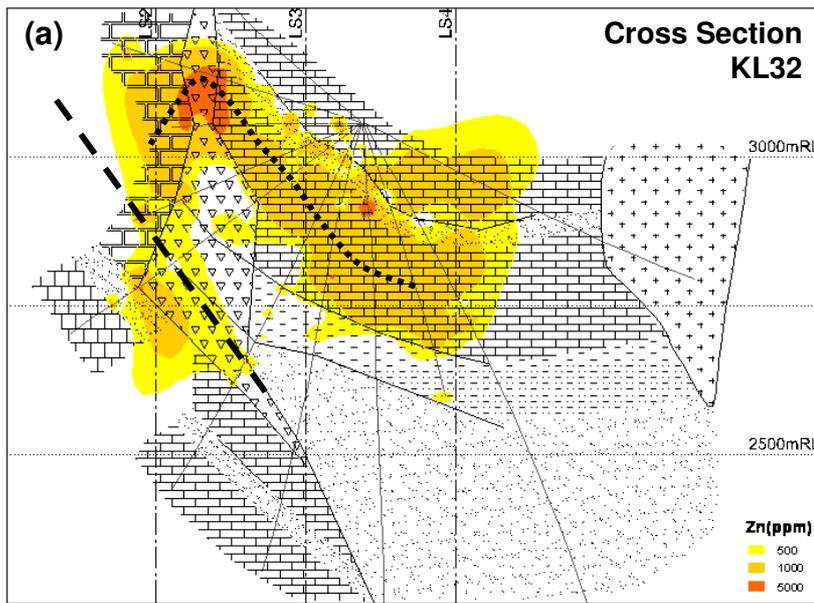


Sections of zinc concentration models overlain on drilling traces and the lithological model described in Chapter 4. The Grasberg contact was provided by Freeport geologists

(a) A cross section through station KL32 clearly shows the zinc mineralisation as a halo around the core copper-gold zone centred on, and continuous about, the Idenberg Fault Zone. The halo appears asymmetric and may be offset, as indicated by the dashed line. However, data is scarce to the left (southwest) of the IFZ.

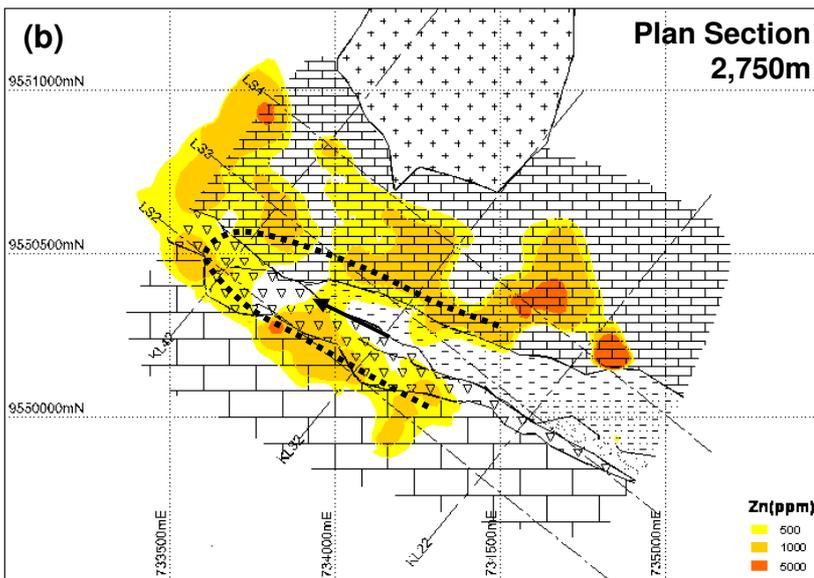


(b) A plan section through 2,750m suggests that the zinc halo plunges northwest, as indicated by the dotted line and arrow.

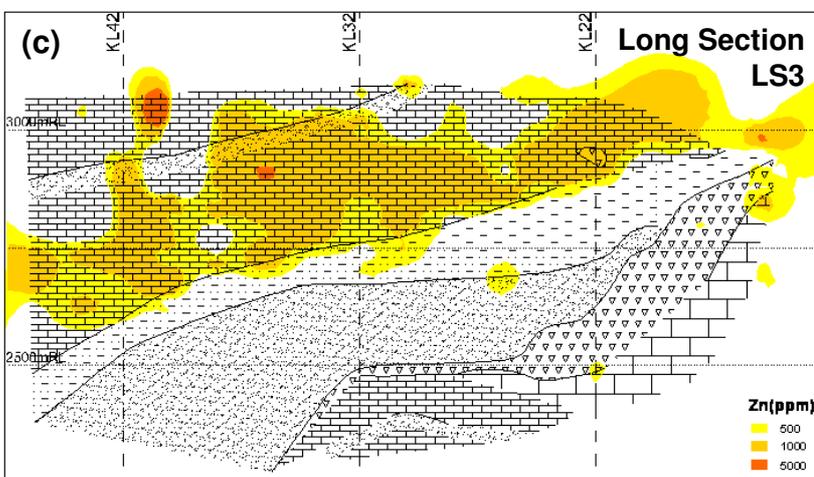


(c) A long section perpendicular to cross sections demonstrates the extent of low-grade zinc mineralisation within the Waripi Limestone as well as its continuity. See (a) & (b) for location.

Figure 5-7 Spatial distribution and structural controls of lead

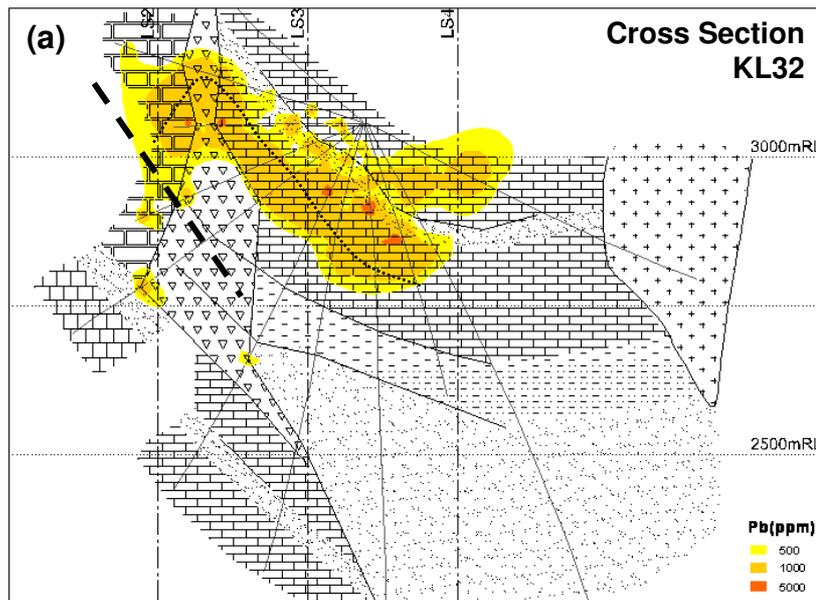


Sections of lead concentration models overlain on drilling traces and the lithological model described in Chapter 2. The Grasberg contact was provided by Freeport geologists. The distribution of Pb closely resembles that of Zn.

(a) A cross section through station KL32 highlights the same halo-like nature of Pb though it is not as concentrated as Zn. Again the halo appears asymmetric but the Pb-halo is continuous across the IFZ. There are indications that the zone of Pb-mineralisation has been truncated at the southwest side of the IFZ (dashed line).

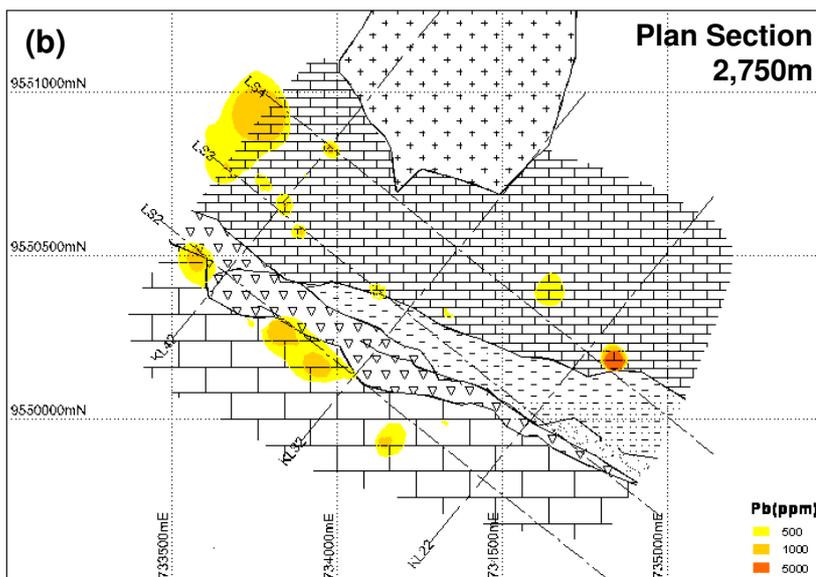


(b) A plan section through 2,750m shows that Pb does not extend down to elevations where zinc is prevalent

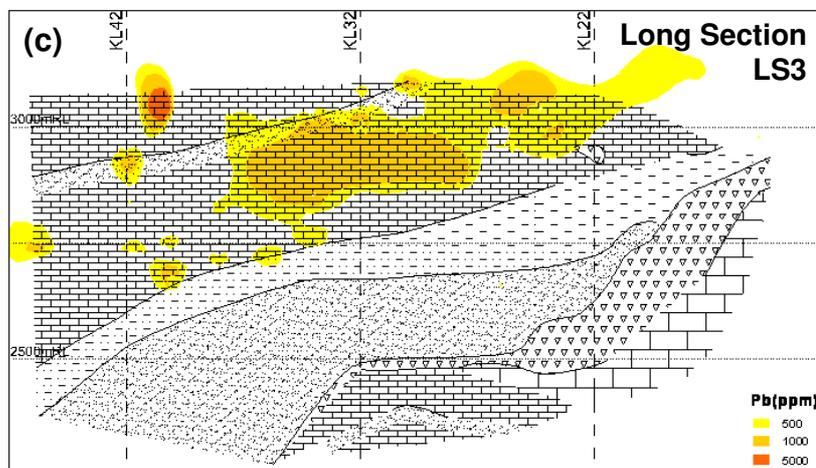


(c) A long section perpendicular to cross sections shows the same association of Pb-mineralisation within the upper Waripi limestone unit. See (a) & (b) for location.

Figure 5-8 Spatial distribution and structural controls of gold

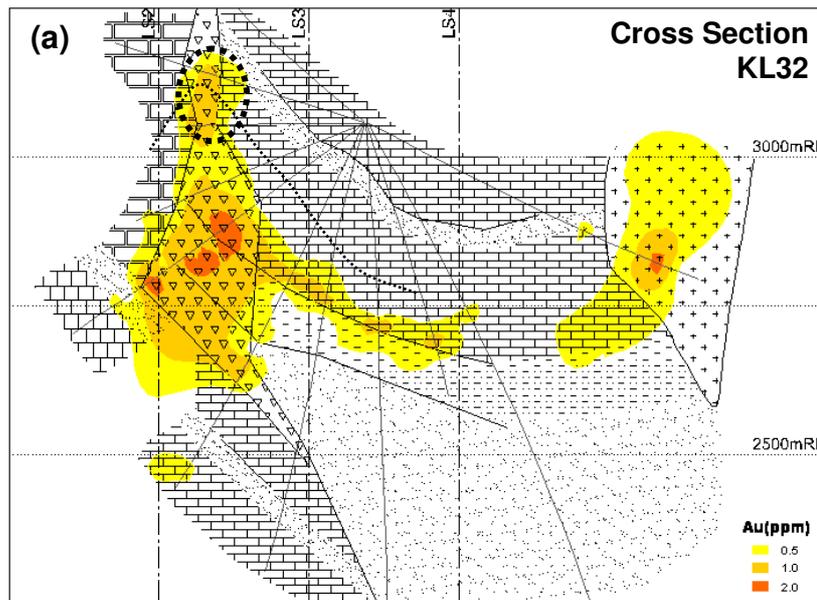

(a) A cross section through station KL32 shows the strong control of Au within an offset in the IFZ. The effect of the Kkel-Tngw contact is also clear. A small concentration of gold (dotted circle) at the Zn-halo hinge mark (dotted line) is independent of Cu.

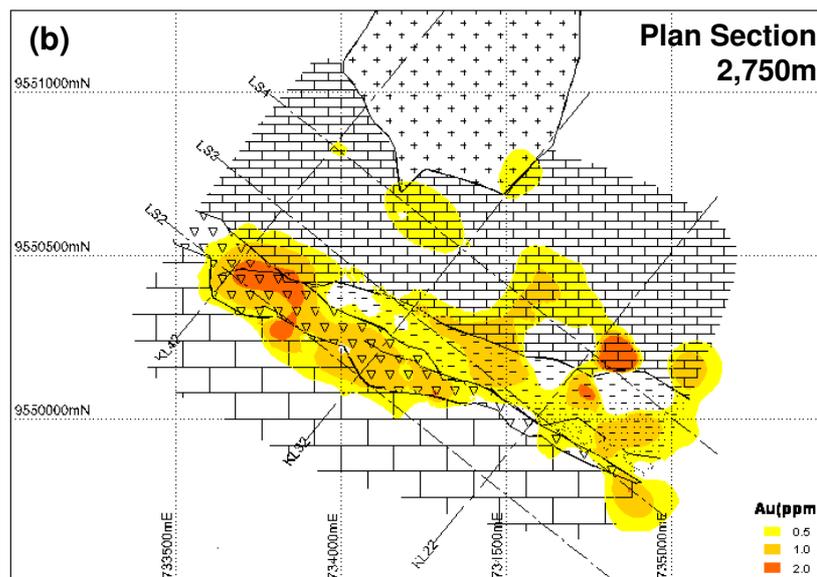

(c) A long section perpendicular to cross sections shows that Au-mineralisation extends the length of drilling within the lower Waripi Limestone and strongest at the eastern end of the deposit. See (a) & (b) for location of sections.



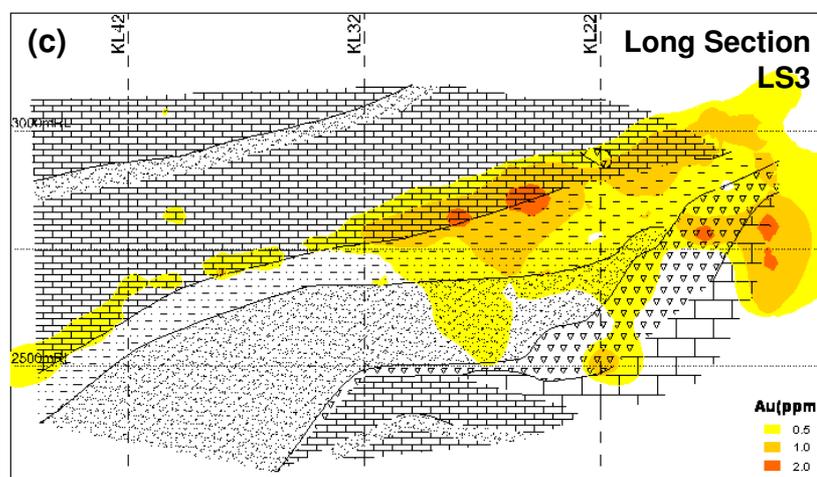



Figure 5-9 Spatial distribution and structural controls of silver

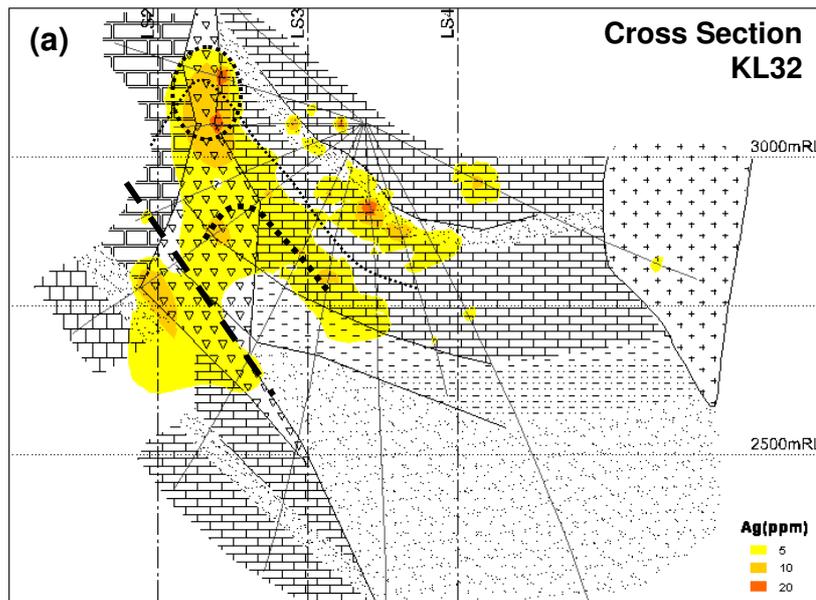

(a) A cross section through station KL32 shows the same halo-like structure (bold dotted line) for Ag concentrations inboard of the Zn-Pb halo (light dotted line). The same suggestion offset at the left of the IFZ is marked (dashed line).

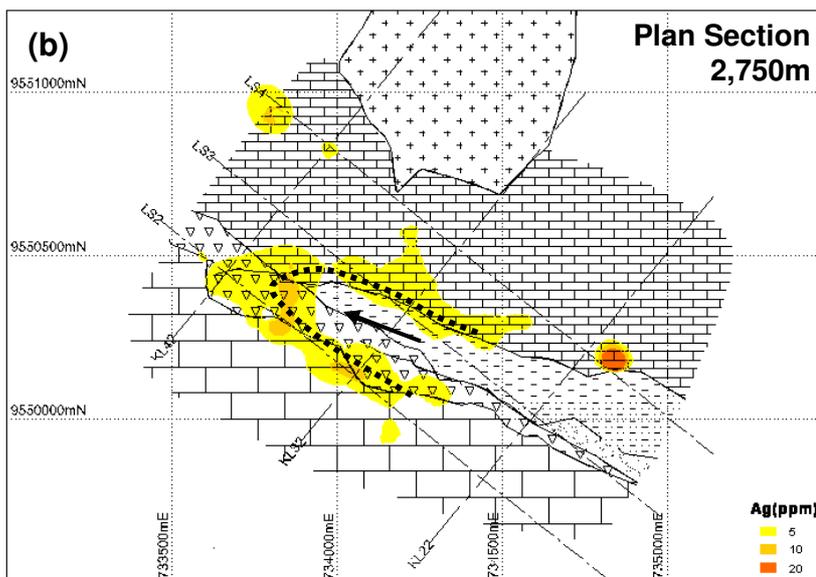


(b) A plan section through 2,750m shows the clearly defined annulus of Ag-mineralisation. The plunging attitude of mineralisation is made clear by dotted line and arrow.

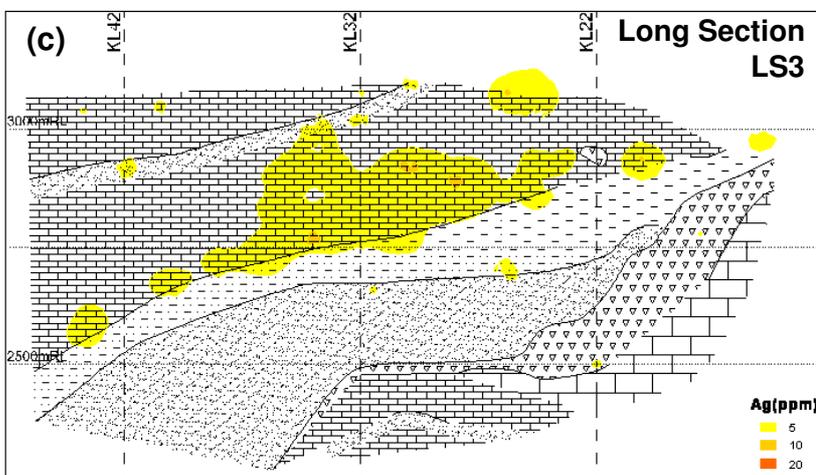


(c) A long section perpendicular to cross sections indicates that elevated silver is concentrated in the lower rather than upper Waripi limestone. See (a) & (b) for location.

Figure 5-10 Spatial distribution and structural controls of arsenic

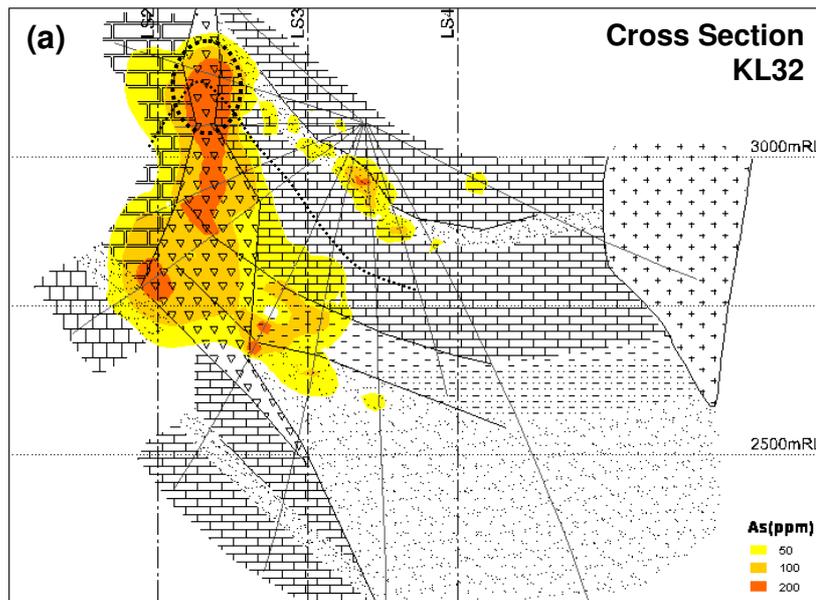


Sections of As concentrations overlain on drilling traces and the lithological model described in Chapter 2. The Grasberg contact was provided by Freeport geologists

(a) A cross section through station KL32 indicates the high elevation of As concentrations in the middle of the deposit. The circle of Au-Ag-Zn-Pb mineralisation in the Zn-Pb halo hinge has been added for comparison.

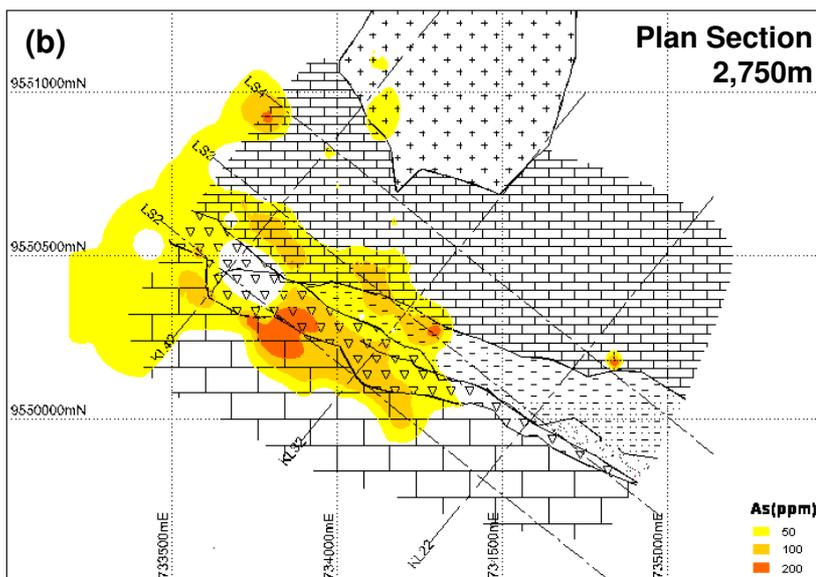


(b) A plan section through 2,750m shows that As occurs at deeper levels to the northwest end of the deposit, indicating a plunge in mineralisation zoning.

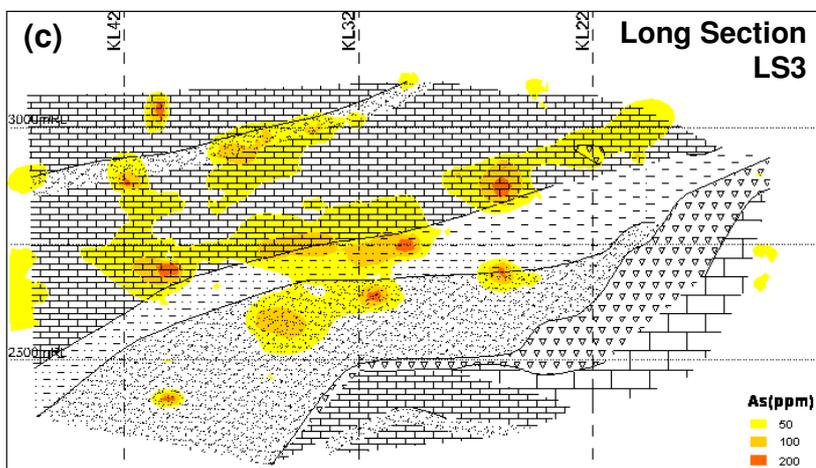

(c) A long section perpendicular to cross sections shows the concentration of As along the base of the Waripi Limestone not apparent in the cross and plan sections. However, unlike copper and gold, As is concentrated above the lower contact, close to the upper skarn contact (Chapter 4). See (a) & (b) for location.

Figure 5-11 Spatial distribution and structural controls of antimony

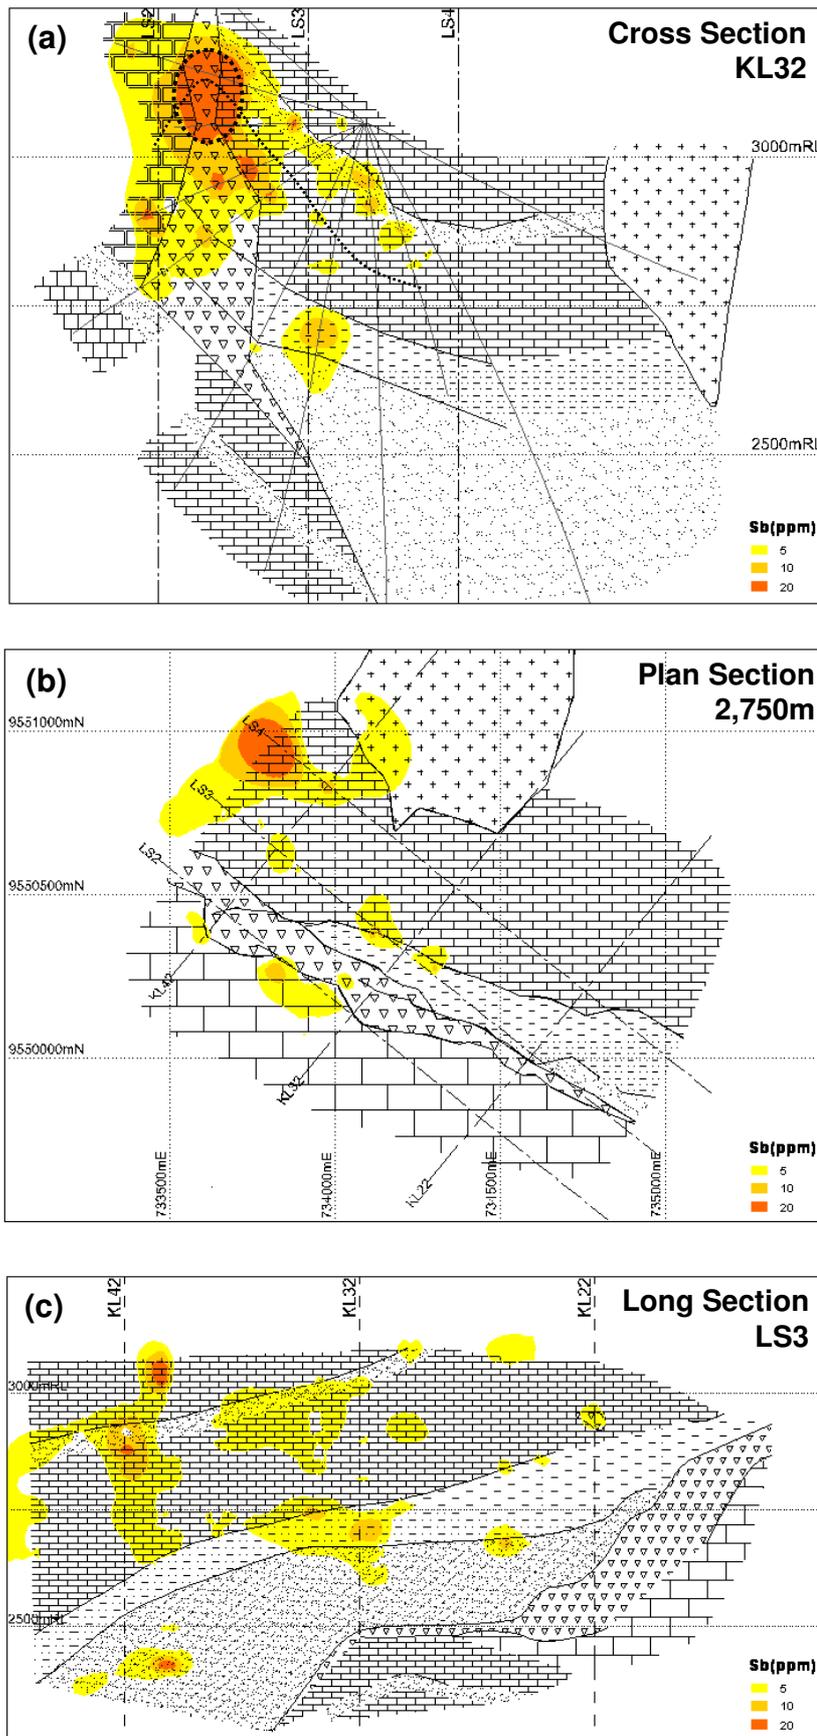

Elevation patterns of metals and ore minerals

Average grades for specific elevation intervals have been generated by compositing all drilling data into 20m elevation windows and plotting metal and mineral abundances against these elevations. Copper and gold are strongly correlated for much of the elevation range of Kucing Liar mineralisation except near the top of the system where gold enrichment extends beyond that of copper enrichment (Figure 5-12). Peak of gold grade (2,800m) is 100m above that for maximum copper grade (2,700m). The decrease in grade from 2,800m to 3,000m occurs over a much smaller interval (200m) than that for increasing grades from 2,200m to 2,700m. Vertical zoning patterns indicate that Cu-Au-Zn correlate in the lower half of the system while high but erratic gold higher in the system is related to equally erratic concentrations of Ag-Zn-Pb and As-Sb (Figure 5-13). Comparisons of mineralogy to metal assays demonstrate variable assemblages involving ore sulphides and gold concentrations (Figure 5-14). Elevation zoning data also demonstrate the veracity of data as the total copper concentrations closely match the average chalcopyrite + covellite abundances (Figure 5-15).

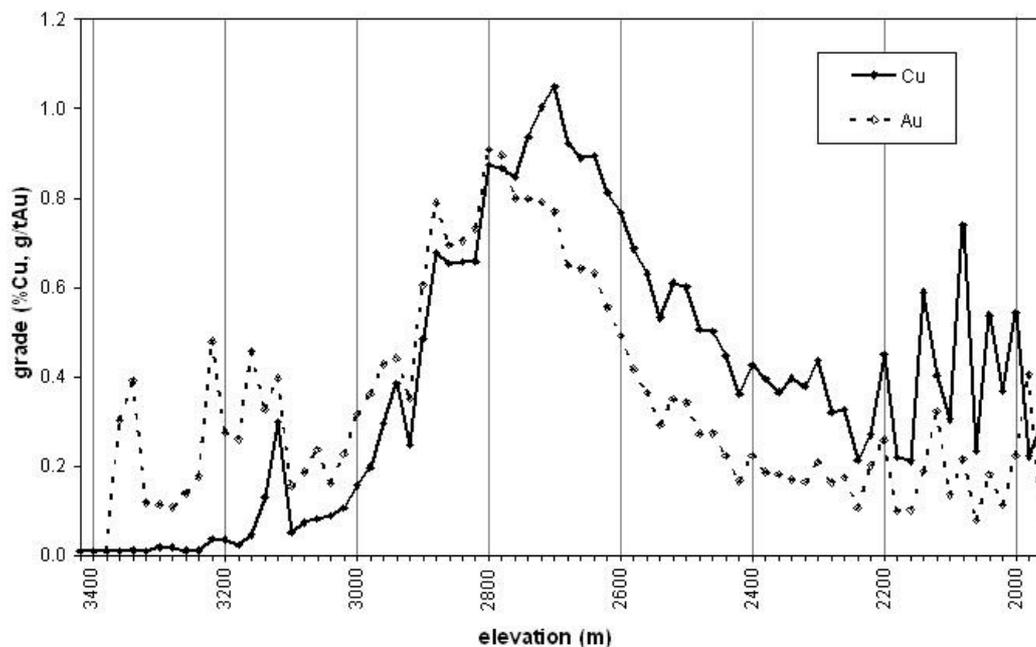


Figure 5-12 Variation of average copper and gold grades relative to elevation

Chapters 1 and 4 have demonstrated that there is no appreciable post-mineralisation tilting of stratigraphy that would affect analysis of elevation zoning in Kucing Liar.

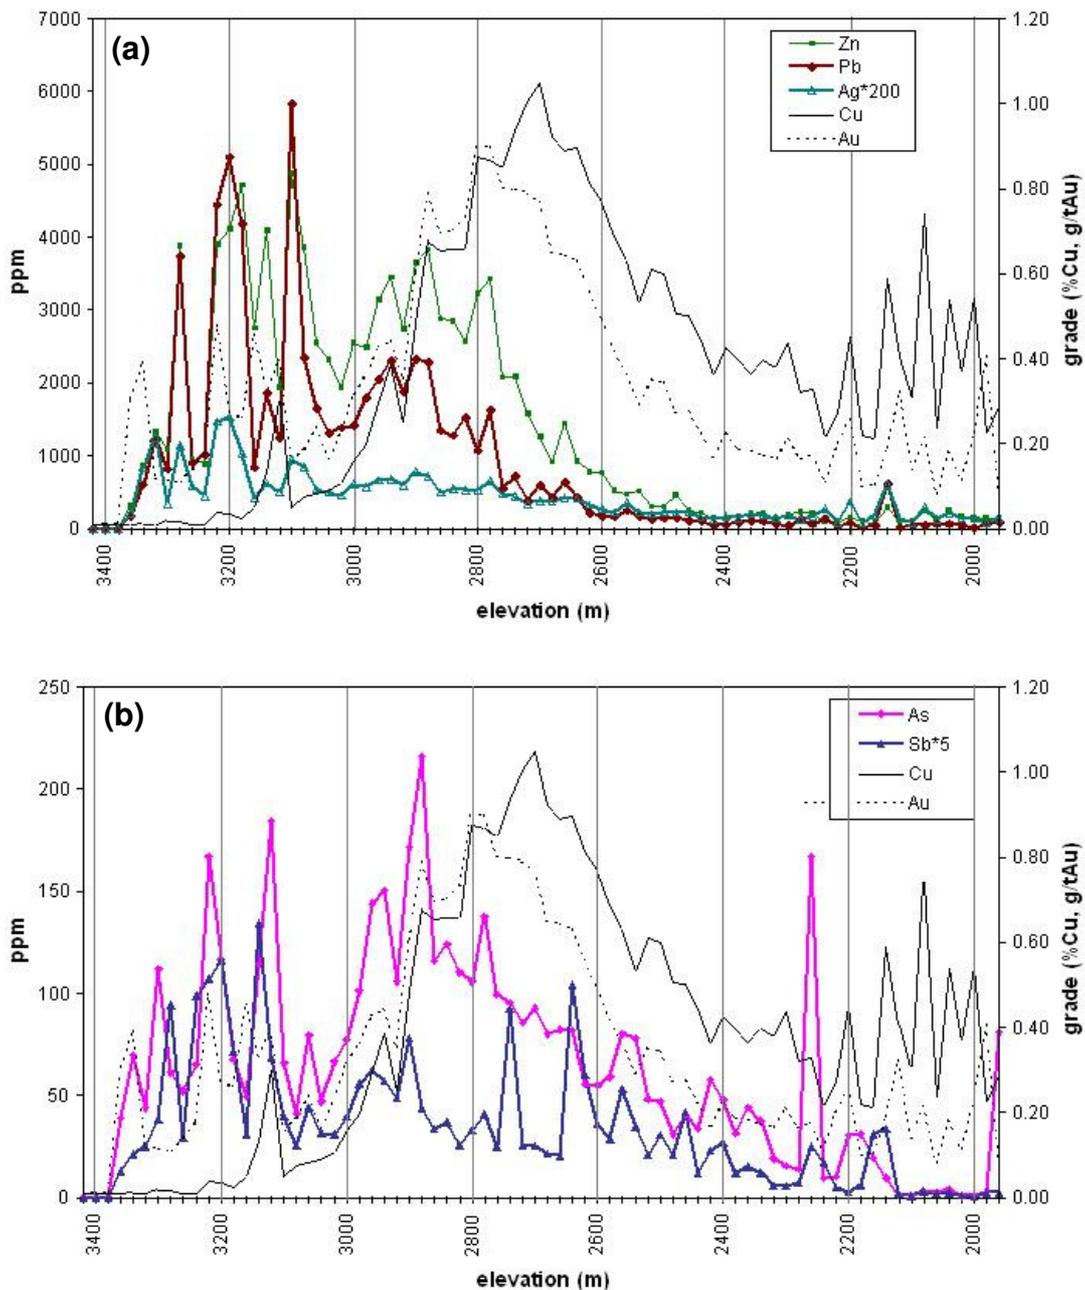


Figure 5-13 Elevation variations of Ag-Zn-Pb and As-Sb relative to Cu-Au

(a) Zinc and lead are plotted along with copper and gold to demonstrate the relationship between base metal mineralisation patterns. Although zinc and lead maxima are at higher elevations than copper and gold, the pattern of increasing grade is very similar for Pb-Zn as for Cu. An erratic zone of high Zn-Pb-Ag grades lies above 3,000m where it is associated with Cu-poor gold mineralisation. (b) A plot of As and Sb demonstrates a similar pattern of erratic high concentration above 3,000m elevation. The plot shows that As is dominant over Sb and closely correlated to Au between 2,800-3,000m, while Sb is relatively more enriched above 3,000m.

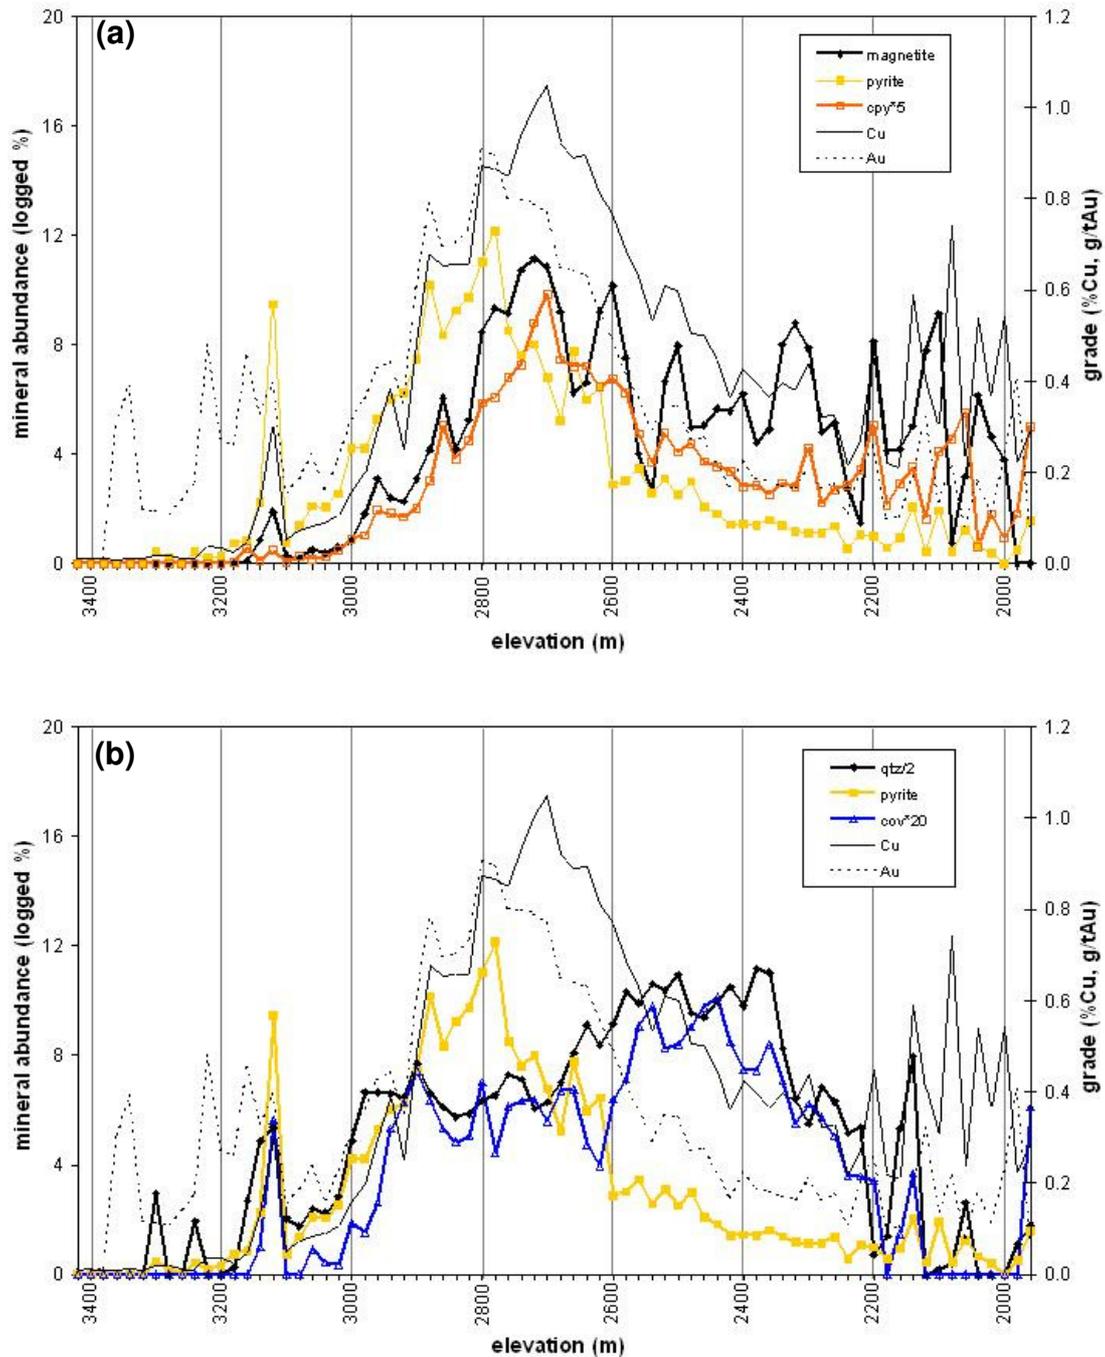


Figure 5-14 Characteristics of chalcopyrite and covellite-bearing ore relative to elevation

These two charts show the elevations variations of copper and gold relative to the main ore-bearing assemblages, namely (a) magnetite \pm chalcopyrite \pm pyrite and (b) quartz \pm covellite \pm pyrite. The two graphs show that magnetite and pyrite have unique maxima and that pyrite may accompany either chalcopyrite or covellite ore. The data show a clear correlation between magnetite and chalcopyrite and between quartz (as alteration) and covellite. The data also show that covellite is more closely associated with pyrite rather than quartz at higher elevations. The plot of pyrite and gold demonstrates that they have maximum concentrations at the same elevations, but that they are unrelated at the highest elevations in the deposit.

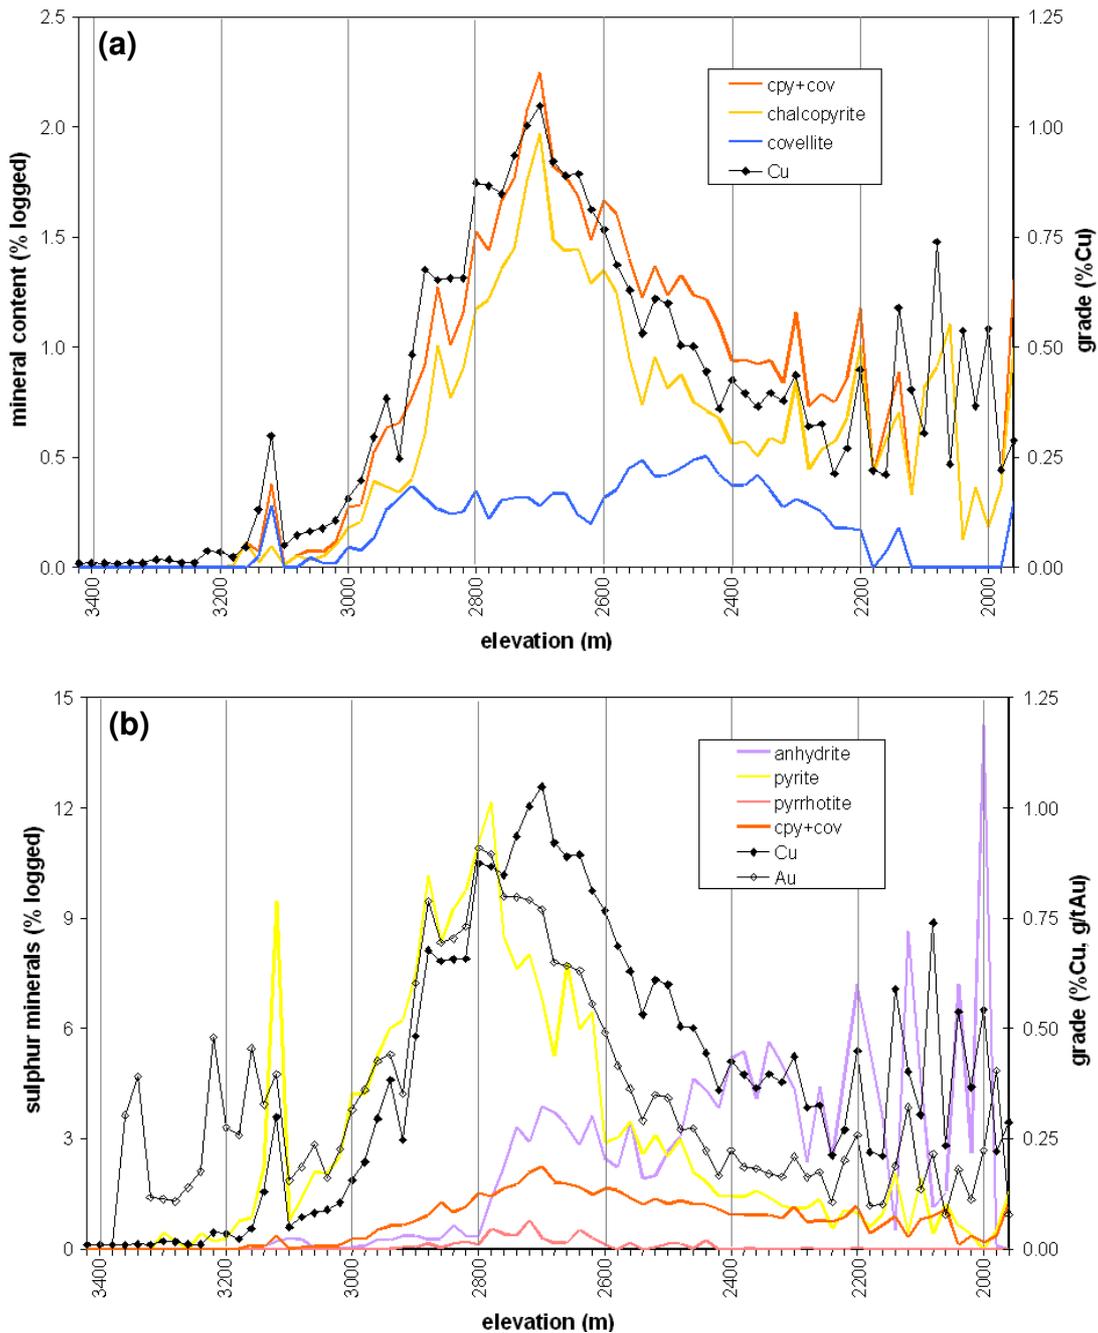


Figure 5-15 Distribution of copper, gold and sulphur phases relative to elevation

(a) A plot of average copper grades for each elevation in combination with chalcopyrite and covellite abundances demonstrates the dominant effect of chalcopyrite on grade. It also demonstrates no apparent elevation effect on covellite distribution. The sum of logged chalcopyrite and covellite matches almost exactly the pattern of copper distribution. (b) A plot of copper and gold grades alongside abundances of sulphur-bearing minerals demonstrates the very close relationship between gold and pyrite, in particular the coincidence of their maxima. The vertical zonation of anhydrite is also made clear, having an antipathetic distribution with pyrite. Mineralogical abundances have been calculated from the average abundance of each mineral type for each elevation range.

5.1.2 Inter-element associations

This section will examine the nature of Kucing Liar mineralisation in terms of the mineral forms and the associated metal suite. Variable copper and gold enrichment and the ratio of the two elements define at least two populations in the assay data. Copper and gold grades reach maximum values of approximately 10%Cu and 10g/tAu respectively and can be divided into two broad categories, a copper-rich (>0.1%) group and a copper-poor group (Figure 5-16). Both groups exhibit a similar range for gold grades, but in the copper-rich group gold grades co-vary with the copper grades, forming a single trend in grade, while for the copper-poor group there is no relationship between copper and gold grades. The co-varying population has a ratio roughly approximating $2\text{Cu}=10,000\text{Au}$, though there is a large scatter of gold grades for a specific copper grade (e.g. at 1% Cu there is a range from 0.2g/t Au to 2g/t Au). It appears that $(\text{Au} \times 10,000)/\text{Cu}$ is higher in higher grade samples, as demonstrated by the trend of covarying data points (Figure 5-16a). As the data are divided into two populations, the analysis of ore deposition will focus of high Cu (>0.1%) and low Cu (<0.1%) varieties.

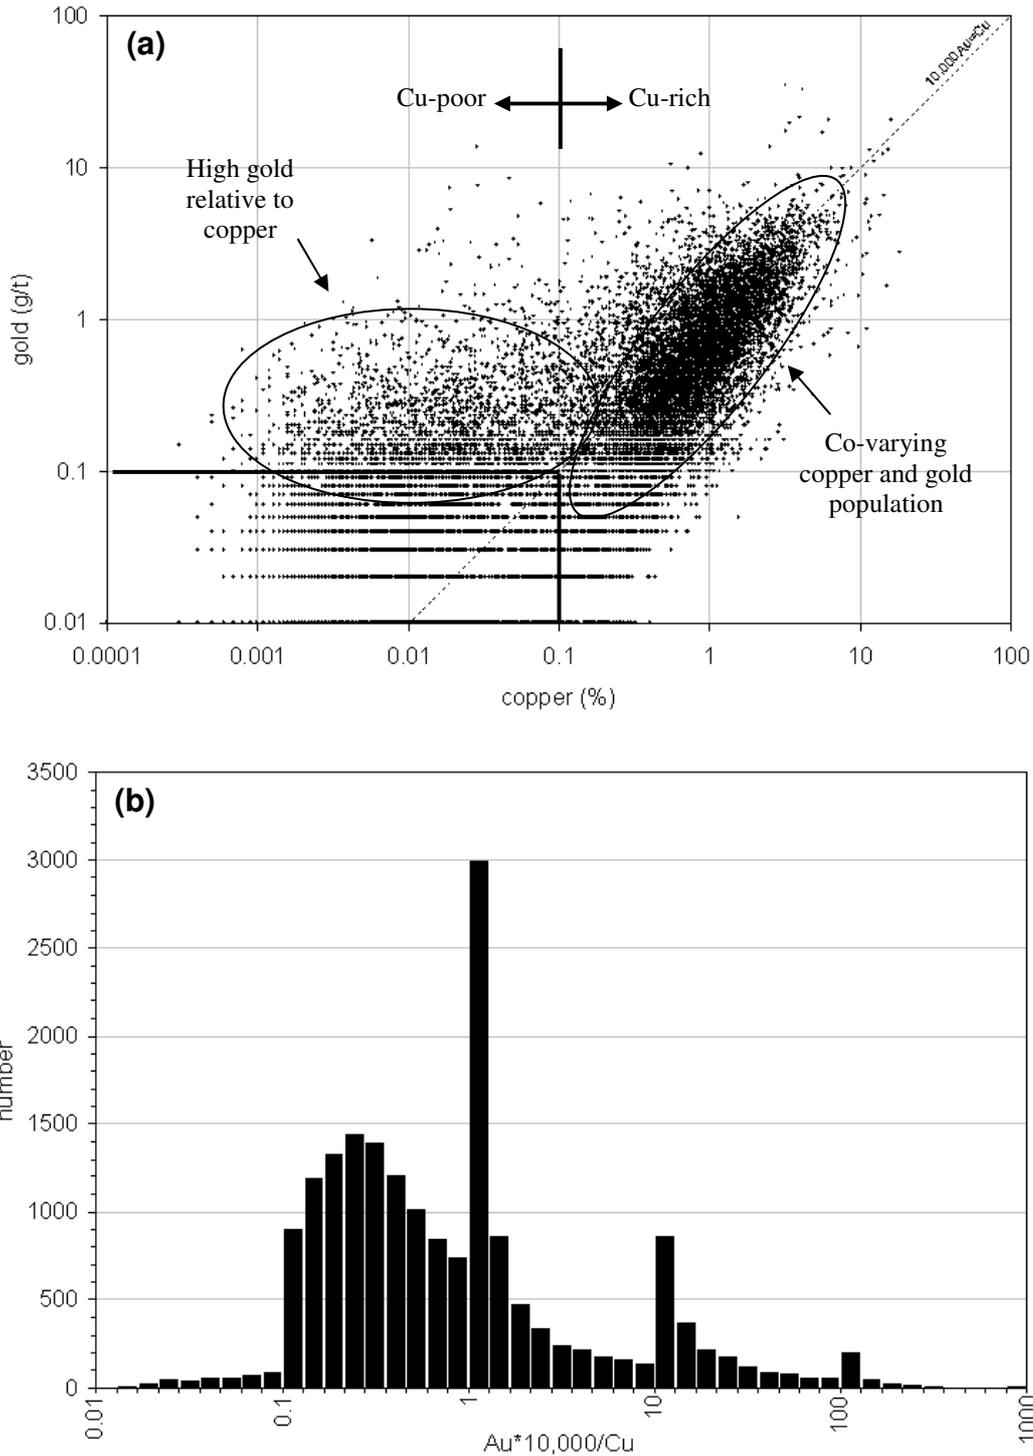


Figure 5-16 Global relationship of copper and gold

(a) Copper-gold plot for all assays ($n=27,290$) illustrating two populations of copper-rich ($>0.1\%$ Cu) and copper-poor ($<0.1\%$ Cu) samples. An ellipse drawn to represent broad trend of the data is steeper than $Au \cdot 10000 = Cu$ line, indicating that the Au:Cu ratio is not constant (b) Frequency histogram of $Au \cdot 10,000 / Cu$ with low-grade samples ($<0.1\%$ Cu or <0.1 g/t Au) extracted ($n=18,351$). The co-varying copper-gold population identified in (a) is apparent in (b) by the symmetrical distribution gold-copper ratios between 0.1 and 1 ($Au \cdot 10,000 / Cu$).

Copper-gold relationships

The two main copper minerals, chalcopyrite and covellite are, in general, mutually exclusive (Chapter 3). As such, each sample interval has been characterised as either chalcopyrite- or covellite-bearing. The average grades of copper and gold for each type of mineralisation (Table 5-1) demonstrate that chalcopyrite-bearing intervals contain roughly ~1.0% more copper than covellite-bearing ones, but more importantly that the average gold grade of chalcopyrite-bearing intervals is almost twice that of those bearing covellite. There is also a third population of samples that contain no visibly identified copper-bearing sulphide. Analysis of the grade data from this group confirms that some of these intervals must have contained copper-bearing sulphides that were not identified (Figure 5-17). As a single sample was used to represent an average of 3m lengths (Appendix V), weak or sporadically-developed mineralisation may not have been represented. Furthermore, sample quality (grainsize and oxidation) may also have obscured copper minerals and overrepresentation of the “no sulphide” group (oxidation is a result of sample storage). The average copper and gold grades of the various alteration mineral assemblages indicate that the more significant ore deposition was closely related to magnetite and pyrite alteration while the remainder of the assemblages are relatively uniformly mineralised (Figure 5-18). These data also indicate that most alteration assemblages except galena-sphalerite the gold-copper ratio $Au*10,000/Cu$ is greater than 1.

Data with low (<0.1% Cu) copper concentrations have uncorrelated gold-copper values and may represent a distinct style of gold-dominant mineralisation. This form of gold enrichment is present in most assemblages except magnetite, biotite, tremolite-actinolite and anhydrite but it is a significant component of quartz and calcite ± magnetite alteration (Figure 5-19). Galena-sphalerite is distinct from other mineral assemblages in relation to low-Cu styles of mineralisation as it is the only assemblage dominated by this style.

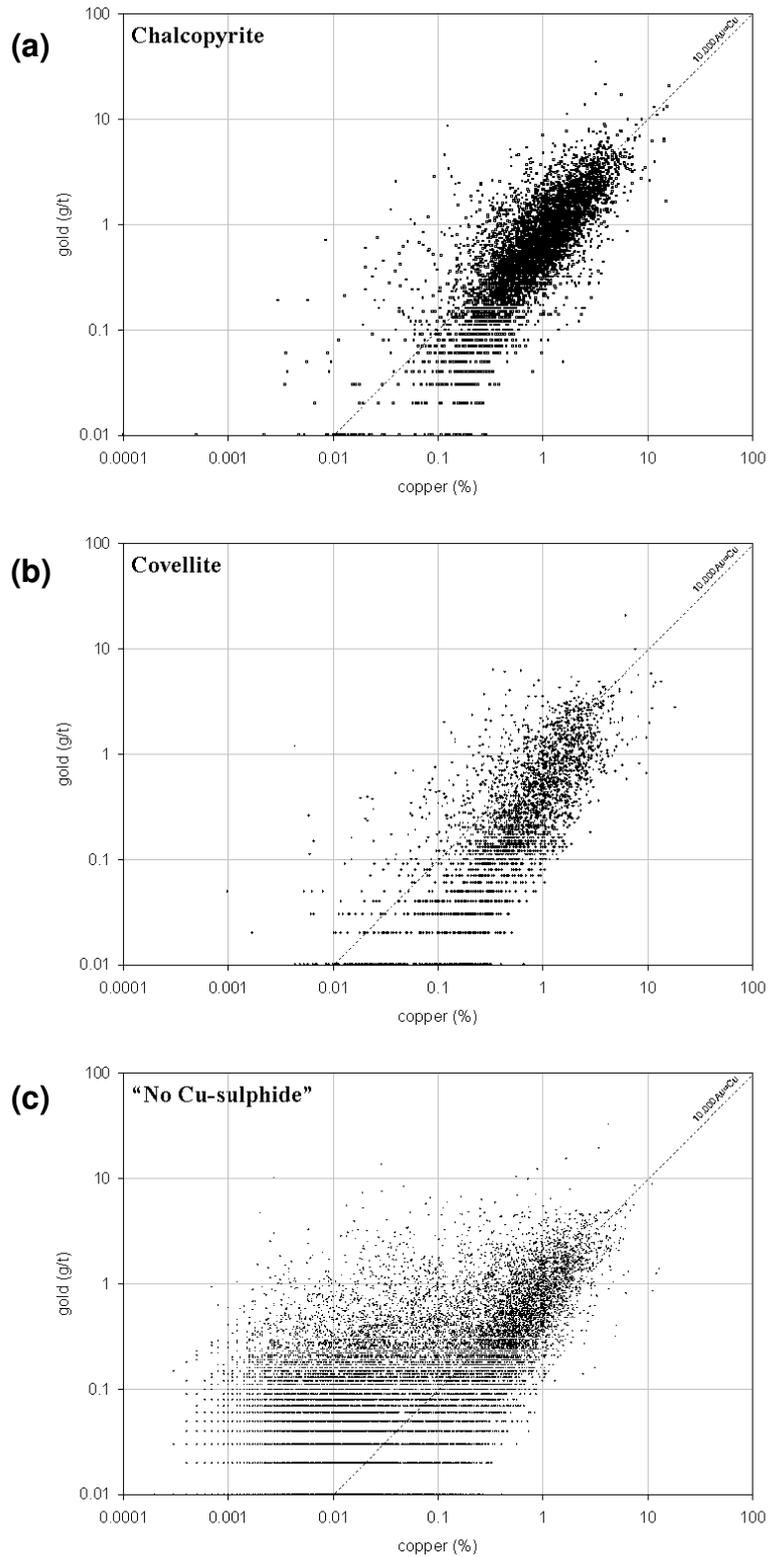


Figure 5-17 Copper and gold distributions in assay populations classified by logged copper sulphide species

The large number of samples in the "no Cu-sulphide" that have similar grade relationships to chalcopyrite and covellite distributions are believed to contain sulphide that has not been recognised. Linear regressions are, $Au(g/t) = 0.78 Cu(\%)$ and $Au(g/t) = 0.52 Cu(\%)$ for chalcopyrite- and covellite-bearing assay intervals respectively.

Table 5-1 Average grade of mineralisation in different mineral associations

	Cu (%)		Au (g/t)		number
	Av.	Std. Dev.	Av.	Std. Dev.	
Chalcopyrite	1.18	1.2	0.99	1.29	5,910
Covellite	0.99	1.1	0.59	0.87	2,868
No sulphide logged	0.42	0.67	0.56	0.89	9,666

Averages are calculated from all samples that are >0.1g/t Au or >0.1% Cu. The presence of chalcopyrite or covellite in a sample interval is usually accompanied by pervasive alteration. Low levels of copper and gold in the "No sulphide logged" (NSL) group confirm the existence of low grade or sporadic mineralisation in this sample population. Samples where no sulphide is observed and logged can be derived from sporadic mineralisation which is not preserved in the skeletal core sample collection, or from oxidation of sulphide minerals.

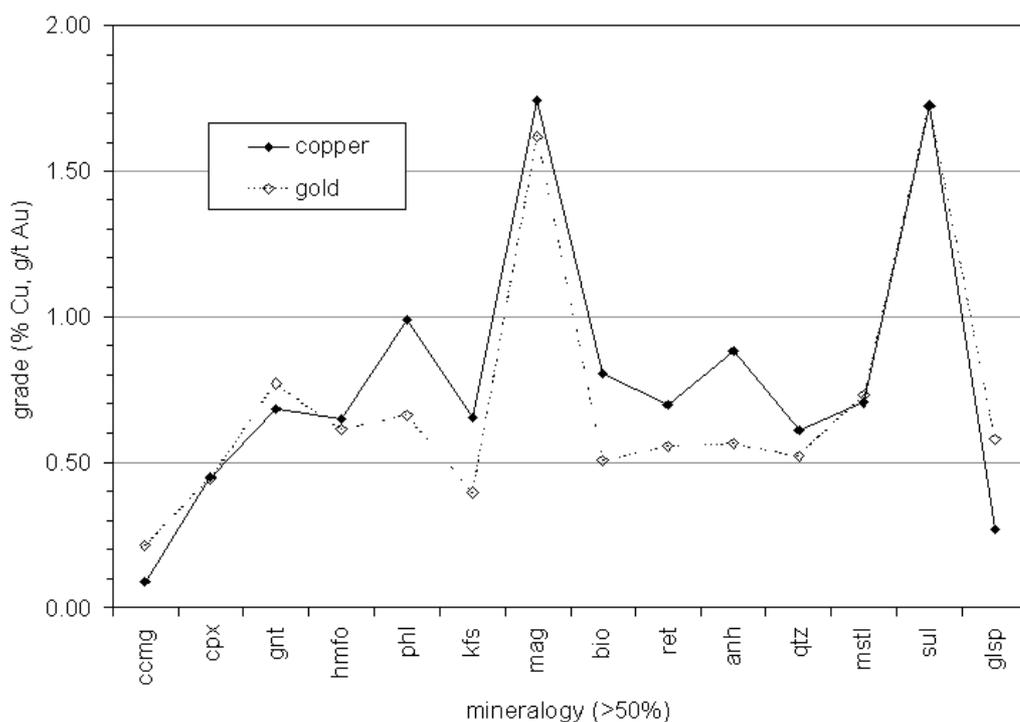
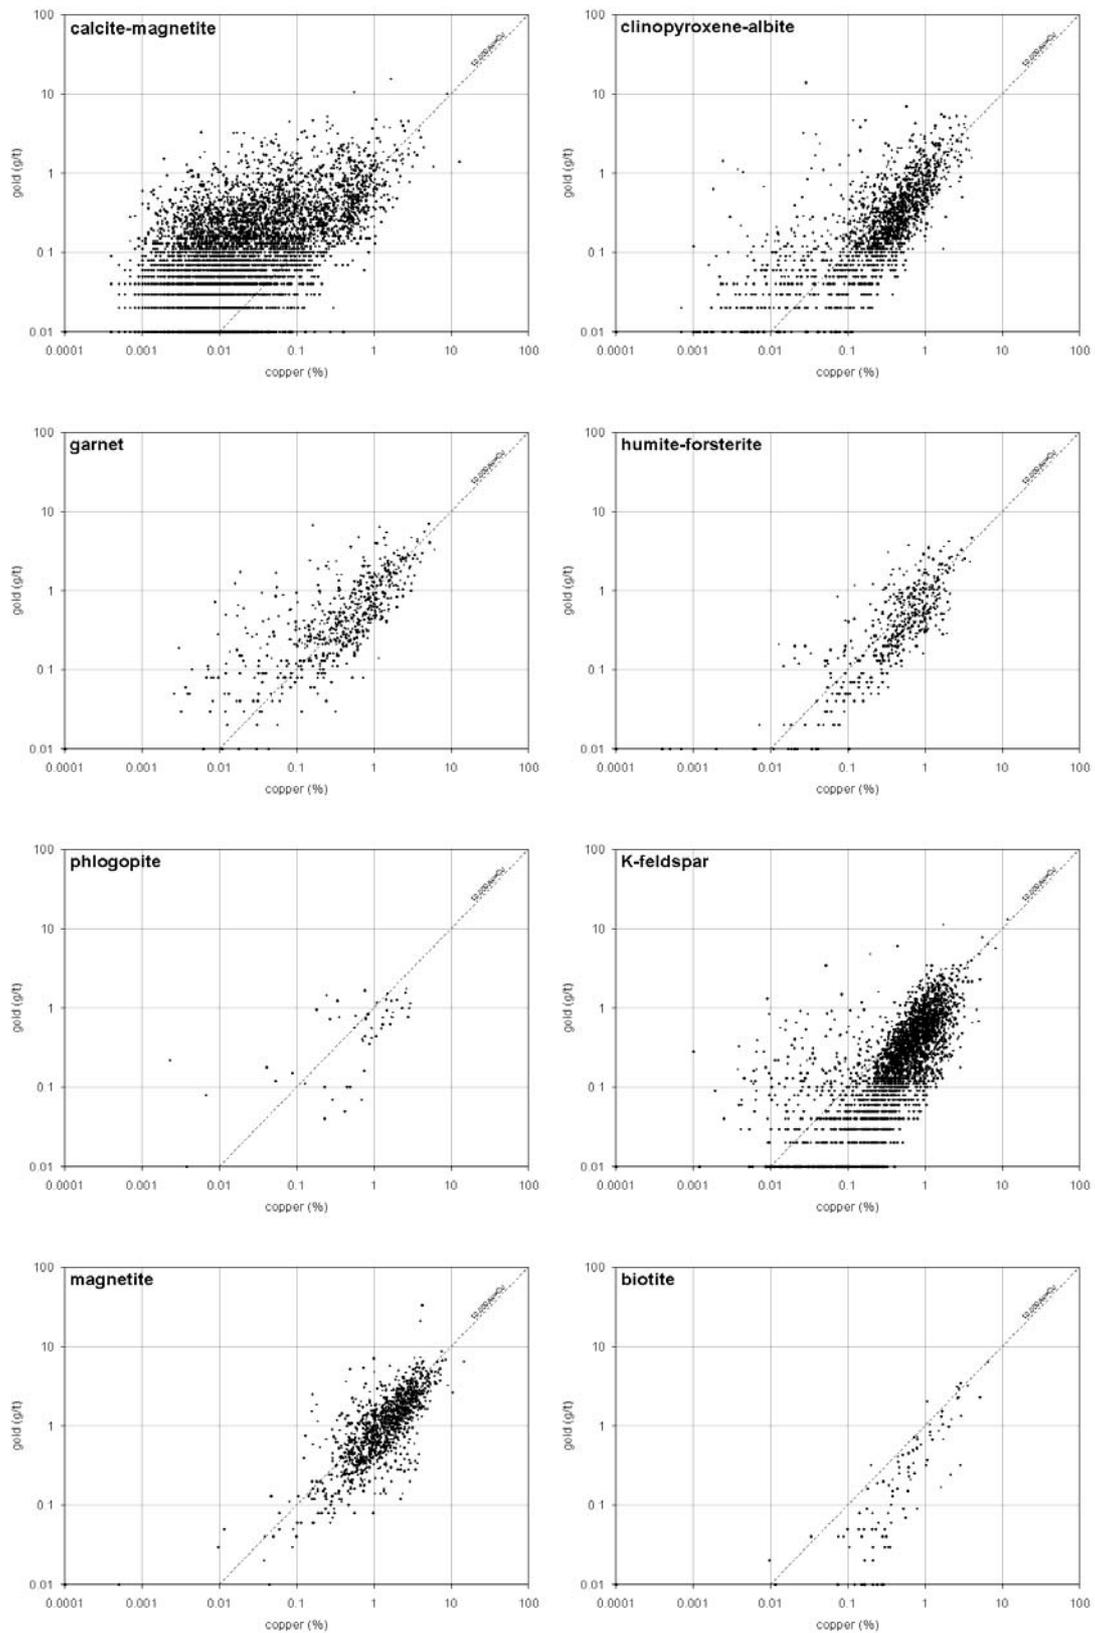


Figure 5-18 Cu-Au grades of assay intervals dominated by various paragenetic associations

Averages values have been extracted from samples containing >50% of the alteration. (anh=anhydrite, bio=biotite, ccmg=calcite ± magnetite, cpx=clinopyroxene, glsp=galena-sphalerite, gnt=garnet, hmfo=humite-forsterite, kfs=K-feldspar, mag=magnetite, msti=muscovite/talc, phl=phlogopite, qtz=quartz alteration, sul= pyrite+pyrrhotite, trsp=tremolite-serpentine).

Figure 5-19 Copper and gold grade distributions in populations classified by dominant paragenetic stage in assay interval



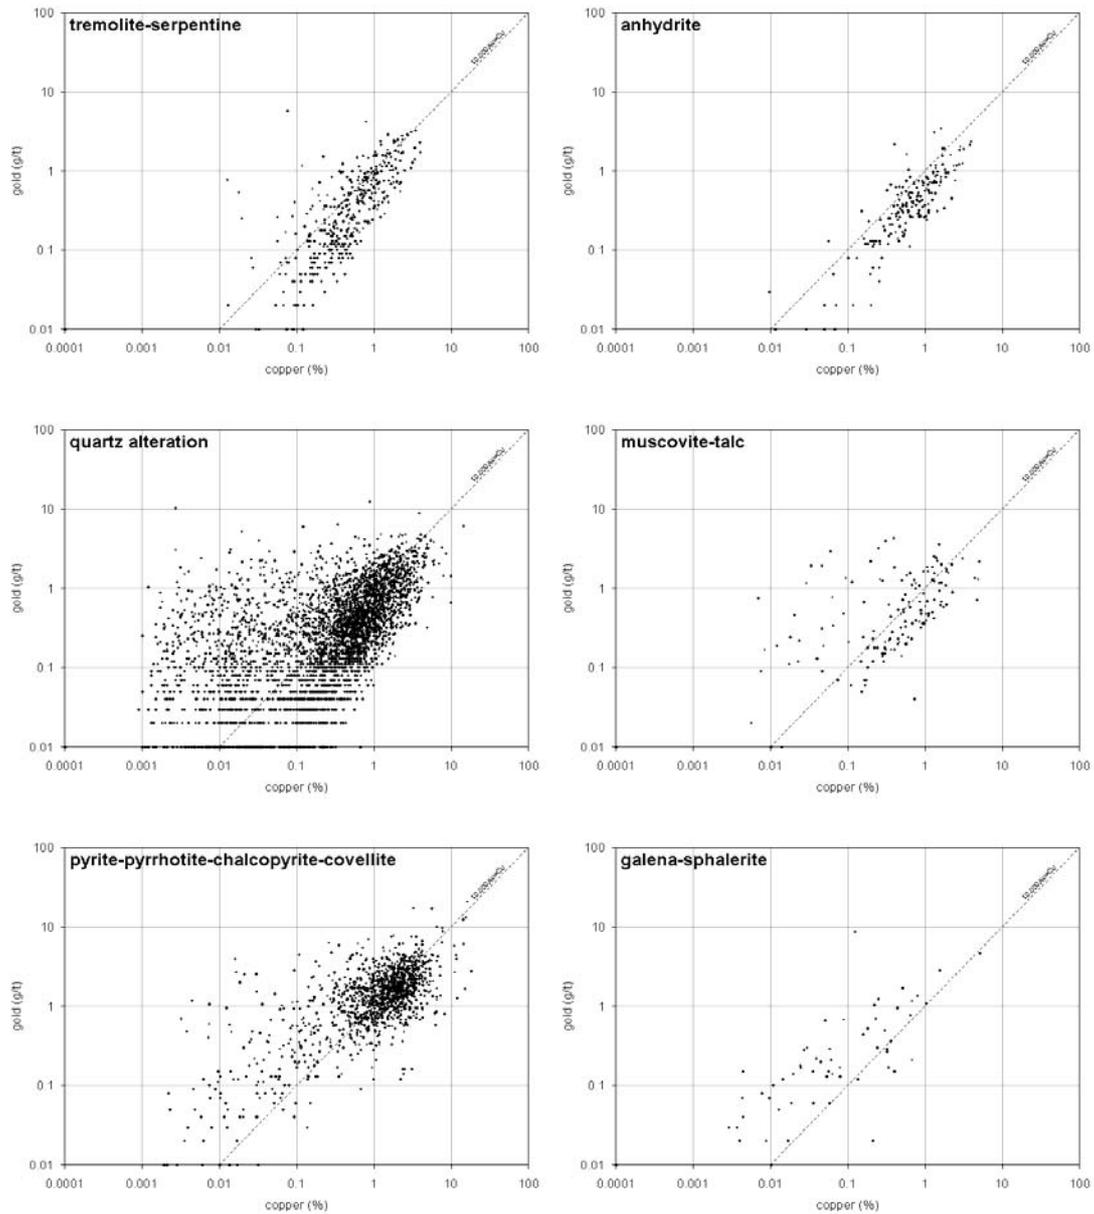


Figure 5-19 (cont.)

Each population includes assay intervals that contain more than >50% of the mineral(s) specified, normalised to 100% of total alteration. A line of $10,000\text{Au}=\text{Cu}$ is included in each plot to distinguish gold-rich and copper-rich samples. Only data from calcite \pm magnetite and the two sulphide associations plot predominantly on the gold-rich side of the graph. Garnet and pyrite-dominated intervals correlate very closely with the $10,000\text{Au}=\text{Cu}$ line, while humite-forsterite, magnetite and anhydrite have non-linear correlation of Cu-Au as indicated by a slightly steeper trend of the data than $y=x$. K-feldspar, biotite, tremolite-serpentine and quartz alteration all have steepest data trends indicating varying gold-copper ratios.

Trace metal relationships

The aim of this section is to identify the element suites that are related to high-Cu, low-Cu, chalcopyrite and covellite-dominant populations. The previous section demonstrated the relationships between copper and gold and showed that there were populations with distinct copper-gold correlations that could be identified in the dataset. Further comparisons were made between copper and gold and the remainder of the elements in the assay suite (Figure 5-20 and Figure 5-21, respectively). It is clear that the copper-rich and copper-poor segregation also holds for other metals. All metals except Co show Cu partitioned into low and high concentration groups. Further data analysis indicates that only As-Sb have very weak correlations with Au for the copper-poor mineralisation (Figure 5-21). Comparisons of average concentrations of the various metals in the different mineralisation groups defined above indicate the basic metal partitioning. Copper-rich mineralisation is enriched relative to copper-poor mineralisation in Au, Co, Mo and Cr, which only has higher average concentrations of Zn and Pb (Table 5-2). In the copper-rich ore, chalcopyrite ore is more enriched in Au, Zn and Co than covellite-bearing ore, which has higher concentrations of As, Sb, Mo and Cr.

The copper-rich population has independent Cu-Au-(Co) and Ag-Pb-Zn-Bi-(Se-Hg) associations while copper-poor mineralisation has As-Au-(Sb-Hg) and Pb-Zn-Ag-(Sb-Se) associations (Figure 5-22). The chalcopyrite-dominant population has Cu-Au-Co and Ag-Pb-Zn-(Se-Sb) where Sb is associated with precious metal and base metal mineralisation. The brackets indicate lower correlation coefficients. Chalcopyrite-dominant ores are characterised by Cu-Au-(Co) with weak associations of Ag-Pb-Se-Hg-Bi-(Zn) while covellite-dominant ores are defined by associations of Cu-Au-(Co-Se), Ag-Pb-Zn-Bi-(Hg) and As-Sb-Hg-(Ag). Mercury is associated with base metal mineralisation in high-Cu populations but is associated with Au-As in the low-Cu population. This indicates that the primary copper association is Cu-Au-Co while base metal mineralisation is an association of Zn-Pb-Ag plus Bi-Sb-Se. A third association defined in the copper-poor population is Au-As-(Sb-Hg).

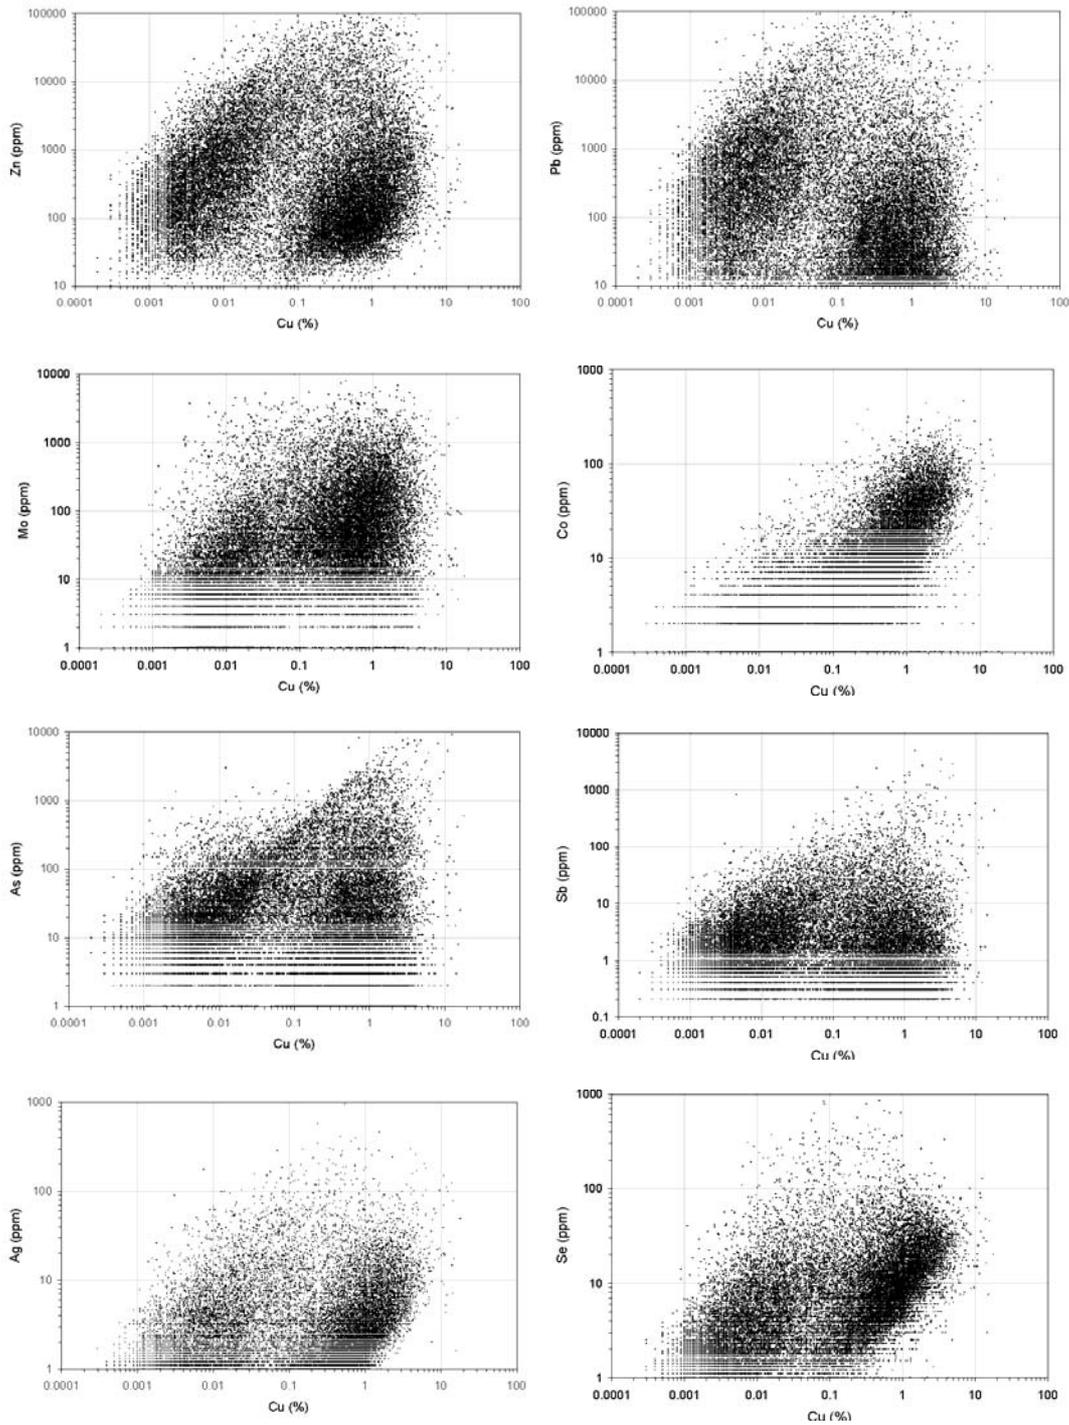


Figure 5-20 Minor element variations with respect to copper

The plots illustrate bimodal distributions of the ratios of copper to other elements. The graphs show that all of the metals except cobalt are divided into high and low copper groups the same as for gold. They also indicate that the average metal grade in low-copper populations is higher for Zn, Pb, and Sb and higher in the high-copper population for Mo, Ag, and Se (see Table 5-2).

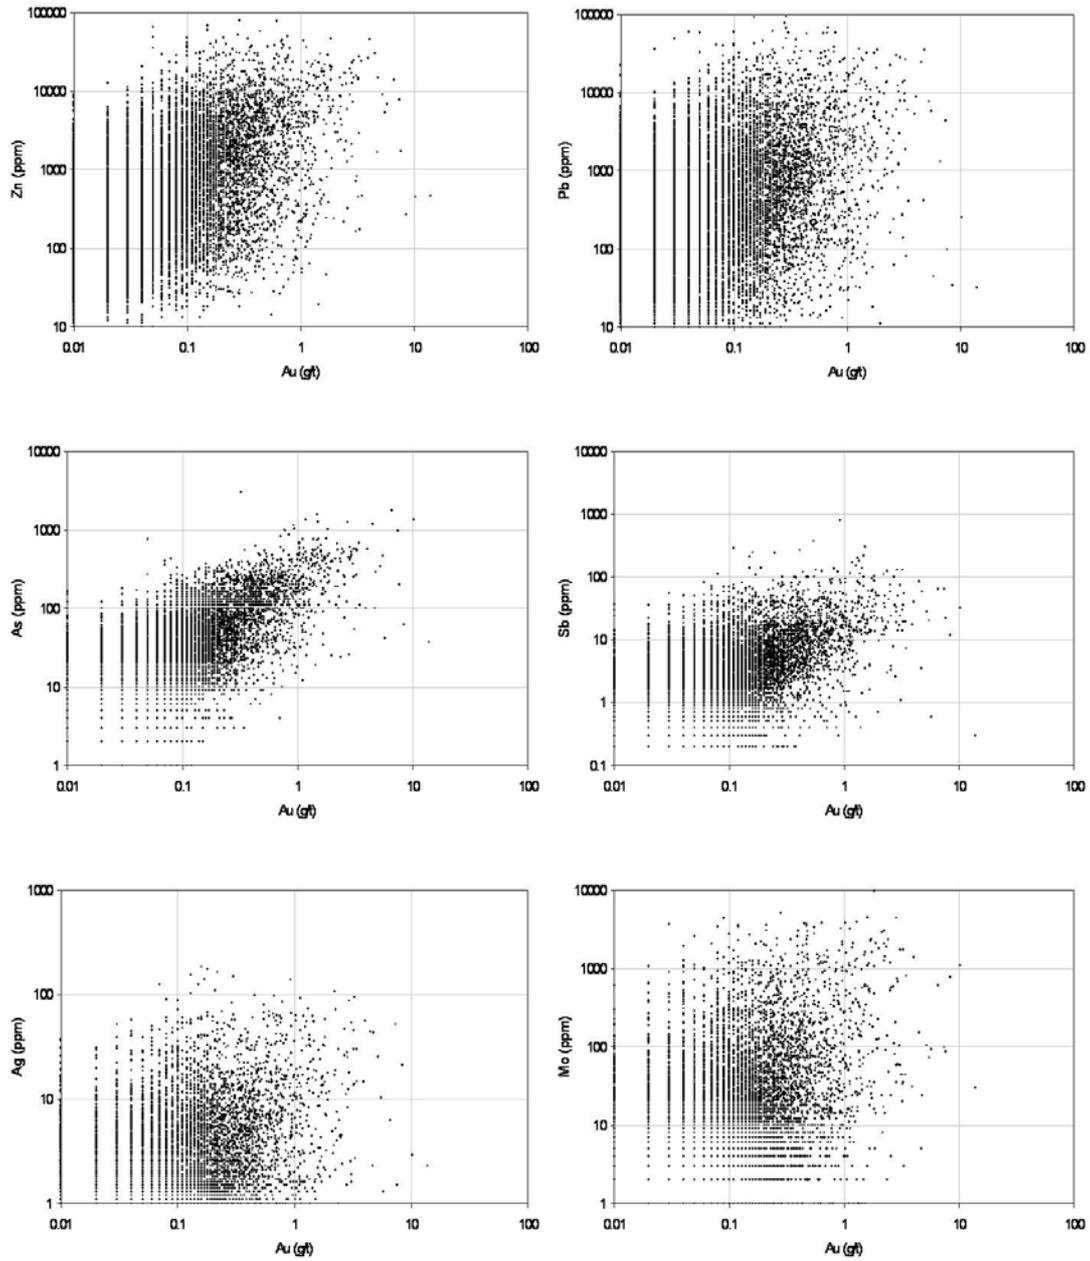


Figure 5-21 Minor element variations of the low-Cu ore sample population with respect to gold
This sample population is derived from the samples that are below 0.1%Cu. The data shows that there are no significant relationships with other metals although As and Sb do form roughly coherent trends with Au.

Table 5-2 Average metal concentrations in assay intervals classified by copper species present

	Total N=26940	High-Cu N=14698	Low-Cu N=3744	Cpy N=5975	Cov N=3177
Cu (%)	0.52	0.94	0.02	1.16	0.93
Au	0.49	0.79	0.35	0.98	0.55
Ag	5.0	6.4	6.55	4.4	5.2
Zn	2,139	2,591	3,464	1,441	902
Pb	1,208	1,106	2,591	425	483
As	94.2	136.3	97	62.9	196.7
Mo	128.5	184.4	136.7	166.8	231.0
Bi	11.3	15.3	12.7	8.9	9.1
Co	13.3	22.5	3.1	26.1	19.1
Sb	8.4	11.1	11.0	3.3	19.9
Se	12.1	16.2	14.7	13.0	13.3
Cr	64.4	85.9	44.2	71.7	142.9
Hg	0.10	0.13	0.20	0.06	0.15
Au/Cu	8.24	0.84	37.43	1.04	0.86

	Cu	Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
Cu	1.00												
Au	0.60	1.00											
Ag	0.15	0.16	1.00										
Zn	-0.01	0.12	0.53	1.00									
Pb	-0.03	0.03	0.68	0.50	1.00								
As	0.17	0.08	0.30	0.14	0.13	1.00							
Mo	0.06	0.06	0.03	0.04	0.01	0.07	1.00						
Bi	0.04	0.10	0.55	0.34	0.21	0.15	0.05	1.00					
Co	0.47	0.38	0.07	0.12	-0.04	0.04	0.06	0.03	1.00				
Sb	0.06	0.02	0.26	0.10	0.15	0.38	0.02	0.07	-0.02	1.00			
Se	0.06	0.10	0.49	0.37	0.35	0.08	0.04	0.53	0.10	0.06	1.00		
Cr	0.01	-0.04	0.01	-0.05	-0.02	0.09	0.05	-0.01	-0.04	0.06	0.00	1.00	
Hg	0.05	0.07	0.45	0.29	0.31	0.36	0.03	0.10	0.00	0.28	0.06	0.05	1.00

Copper > 0.1%

	Cu	Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
Cu	1.00												
Au	0.18	1.00											
Ag	0.21	0.23	1.00										
Zn	0.27	0.25	0.60	1.00									
Pb	0.18	0.17	0.72	0.76	1.00								
As	0.27	0.55	0.29	0.31	0.22	1.00							
Mo	0.21	0.24	0.06	0.08	0.03	0.27	1.00						
Bi	0.14	0.10	0.29	0.27	0.14	0.12	0.13	1.00					
Co	0.36	0.15	0.03	0.09	0.01	0.16	0.17	0.07	1.00				
Sb	0.20	0.30	0.42	0.37	0.36	0.44	0.11	0.06	0.07	1.00			
Se	0.15	0.13	0.46	0.35	0.43	0.16	0.05	0.39	0.08	0.18	1.00		
Cr	0.26	0.12	0.02	-0.01	0.00	0.13	0.15	0.03	0.19	0.07	0.04	1.00	
Hg	0.10	0.41	0.21	0.27	0.16	0.43	0.12	0.04	0.06	0.40	0.09	0.08	1.00

Copper < 0.1%

	Cu	Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
Cu	1.00												
Au	0.68	1.00											
Ag	0.32	0.30	1.00										
Zn	0.02	0.10	0.39	1.00									
Pb	0.00	0.04	0.56	0.48	1.00								
As	0.11	0.11	0.30	0.20	0.24	1.00							
Mo	0.07	0.04	0.03	0.04	0.00	0.08	1.00						
Bi	0.05	0.09	0.32	0.24	0.17	0.10	0.04	1.00					
Co	0.50	0.40	0.22	0.19	-0.02	0.09	0.05	0.03	1.00				
Sb	0.02	0.02	0.31	0.16	0.25	0.25	0.00	0.05	-0.01	1.00			
Se	0.22	0.23	0.42	0.41	0.51	0.16	0.05	0.52	0.27	0.07	1.00		
Cr	0.01	0.01	0.05	-0.02	0.03	0.08	0.02	0.00	-0.06	0.08	0.00	1.00	
Hg	0.03	0.05	0.49	0.34	0.54	0.33	0.02	0.09	0.03	0.34	0.18	0.08	1.00

Chalcopyrite > 1%

	Cu	Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
Cu	1.00												
Au	0.59	1.00											
Ag	0.33	0.29	1.00										
Zn	0.08	0.19	0.55	1.00									
Pb	0.04	0.10	0.60	0.65	1.00								
As	0.25	0.14	0.43	0.14	0.13	1.00							
Mo	0.12	0.11	0.02	0.02	0.02	0.06	1.00						
Bi	0.18	0.25	0.57	0.50	0.42	0.21	0.02	1.00					
Co	0.43	0.41	0.13	0.12	0.01	0.08	0.09	0.12	1.00				
Sb	0.14	0.06	0.46	0.09	0.08	0.55	0.01	0.18	0.00	1.00			
Se	0.41	0.46	0.37	0.35	0.19	0.18	0.08	0.38	0.55	0.08	1.00		
Cr	-0.08	-0.04	-0.04	-0.06	-0.04	0.01	-0.02	-0.05	0.03	0.00	-0.01	1.00	
Hg	0.19	0.14	0.50	0.26	0.27	0.56	0.06	0.23	0.09	0.57	0.16	-0.01	1.00

Covellite > 1%

Figure 5-22 Correlation coefficients for significant sample populations in Kucing Liar

The chalcopyrite and covellite >1% groups are a subdivision the >1% copper group. Different colours are used to identify individual associations. Red-orange is used to identify copper correlations, blue-cyan are used to identify Pb-Zn associations, and yellow is used to highlight arsenic correlations.

5.2 INTERPRETATION OF METAL ASSAY DATA

The discussion will be divided into two parts, the first will be concerned with interpreting the data supplied in the chapter, in terms of mineralisation packages and the sequence of events. The second section will examine models for processes of metal precipitation from a hydrothermal fluid in light of metal associations found at Kucing Liar.

5.2.1 Defining the mineralisation process through metal associations

The first part of the discussion of results is a summary of the mineralised ore packages, their metal assemblages, and the relationships between them. In some instances, data from this chapter are integrated with the mineral assemblage relationships from Chapter 3 as well as the mineral assemblage distributions from Chapter 5. The assay data provide further definition of the mineralisation process. The differences and similarities between copper mineralisation forms as well as the partitioning of gold between individual ore packages are of particular interest. Kucing Liar mineralisation is dominated by copper and is accompanied by economic gold concentrations. Copper and gold are closely associated with each other and form a core zone that is hosted within a fault jog and along specific stratigraphic contacts adjacent to the fault. Presumably, metal-carrying fluids were channelled into the Idenberg Fault Zone and migrated to complex intersections of fault elements with pre-existing heterogeneities created by a transition from massive sandstone to thinly bedded limestone. Around this Cu-Au core is a zoned complex of Ag-Pb-Zn though in subeconomic concentrations. Small concentrations of Au outside the main zoned system are associated with As-Sb, which appear to be associated with pyrite and base metal (Zn-Pb) mineralisation.

Styles of mineralisation

Ore deposition in the two copper sulphide-bearing assemblages have similar primary metal associations of Cu-Au (Zn-Pb) though they have individual trace element associations as chalcopyrite ores have higher concentrations of Au, Zn, and Co, while covellite ores have higher

Mo, As, Sb and Hg average concentrations. There remains no definitive constraint for the temporal relationship between chalcopyrite-bearing and covellite-bearing ores. The shape of the 1% Cu contour is not related to the individual distributions of chalcopyrite or covellite (Figure 5-23). Gold appears to have three separate associations. It is associated with chalcopyrite and Cu in the lower elevations, but is then strongly associated with pyrite and As before passing to a Au-As-Sb association at the top of the deposit where it is associated with highest Ag-Pb-Zn-(Bi) mineralisation (Figure 5-13 and Figure 5-14), though the association is not strong (Figure 5-21 and Figure 5-22). There is a strong spatial association between covellite and arsenic as well as pyrite and arsenic. Arsenic-rich covellite mineralisation may result from the inclusion of enargite, which is known to occur with covellite (Chapter 3). Arsenic-rich pyrite forms from substitution of As into the crystal lattice of pyrite, which increases its capacity to carry Au (Reich *et al.*, 2005). Due to the time-consuming requirements of the existing research program, no detailed microchemical study of sulphides was performed in this research in order to comprehensively characterise the occurrence of gold (this would make a particularly enlightening study for future researchers). It is expected that gold occurs as inclusions within chalcopyrite or pyrite in the lower zone, but may be refractory where hosted in arsenic pyrite in the upper zone and possibly as substitutions of tennantite-tetrahedrite in the topmost zone.

Zoning patterns

The Cu-Au core comprises both chalcopyrite and covellite-bearing mineralisation, where covellite occupies a central location within the major offset of the Idenberg Fault Zone (Figure 5-23). There is a clear structural relationship between chalcopyrite and covellite-bearing rocks. This structural association also extends to pyrite concentrations, which are also associated with the Idenberg Fault Zone offset. Chapter 3 indicated a general temporal progression of sulphide from chalcopyrite to covellite, then pyrite and lastly galena-sphalerite. A chalcopyrite ± pyrite has precipitated Cu-Au-Co, and was accompanied soon after by a spatially distinct covellite ± pyrite package with similar metal assemblage but with a greater proportion of copper. These styles of mineralisation changed to a pyrite-dominant Au-As ± Ag style of mineralisation. This precious

metal package changed downflow (up elevation) to an Au-Sb-As package, which is suspected to be in the form of tennantite-tetrahedrite. A shell of Pb-Zn formed about the pyrite, chalcopyrite and covellite core in the form of galena-sphalerite.

5.2.2 Metal complexes and ore precipitation


An outward pattern of Cu-Au, and Ag-Zn-Pb may be related to the solubility of these metals in chloride solutions. Published work (Hemley et al., 1992) indicates that at the same temperature, there is a progression of increasing solubility from Fe→Cu→Zn→Pb. The solubility of all of these metals decreases at a steady rate with decreasing temperature. The solubility data neatly predicts the zoning of metal enrichment found at Kucing Liar. This assumes that all metals are carried as a chloride complex and that the solution is saturated with respect to chloride-complexed minerals. It is assumed that gold is carried in an Au-Cl complex although experimental work has suggested that gold may be transported and even sequestered at elevated temperatures and pressures by H₂S ligands rather than chloride (e.g. Loucks and Mavrogenes, 1999). If gold were to be complexed as a bisulphide complex rather than chloride, it would require a different set of changes to the hydrothermal conditions in order for precipitation to take place, as it is known that the factors affecting solubility of Cl-complexes are different, and sometimes opposite to those affecting HS-complexes (Barnes, 1979).

A second form of metal complex is in the form of bisulphide, which may carry Au, As, and Sb in solution (Crerar and Barnes, 1976; Heinrich et al., 1992; Bessinger and Apps, 2003). Some workers have also suggested that Cu is preferentially partitioned into bisulphide solutions, but recent experiments have indicated specific conditions must prevail for bisulphide to be preferred over chloride for copper complexing (Mountain and Seward, 2003). It is significant that Fe is not transported as a bisulphide complex (Crerar and Barnes, 1976) as this implies that the Fe, Cu and possibly Au in the pyrite mineralisation package precipitated from chlorine solutions. Gold is more likely to have been precipitated from bisulphide rather than chloride as experiments by Loucks and Mavrogenes (1999) found that “Au-Cl complexes are not important in pyrite-



saturated brines”, which these fluids are expected to be given that they have deposited locally abundant pyrite. The change from Cu-Au to precious metals may point to a change in the state of the hydrothermal system as copper transport is more favoured in oxidised conditions whereas gold transport can occur under oxidised or reduced conditions (Rowins, 2000). Finally, the fluids that deposited Au-Sb-As at the upper portions of the base metal zoned system most likely carried the metals as bisulphide complexes (Bessinger and Apps, 2003).

This chapter has shown that the Kucing Liar mineralised zone is a progressively zoned pattern of overlapping base and precious metals. It is presumed that the same fluid has carried the metals from the original source due to the close temporal and spatial relationships of the ore minerals and metal suite. The interpretation provided here implies a change in fluid conditions, from chloride-dominant to bisulphide-dominant, which favours the transport and precipitation of distinct metal assemblages, changing from Cu-Au-Ag-Zn-Pb to Au-As-Sb.

Figure 5-23 Zoning of ore sulphides, pyrite, chalcopyrite and covellite and Cu-Au-As

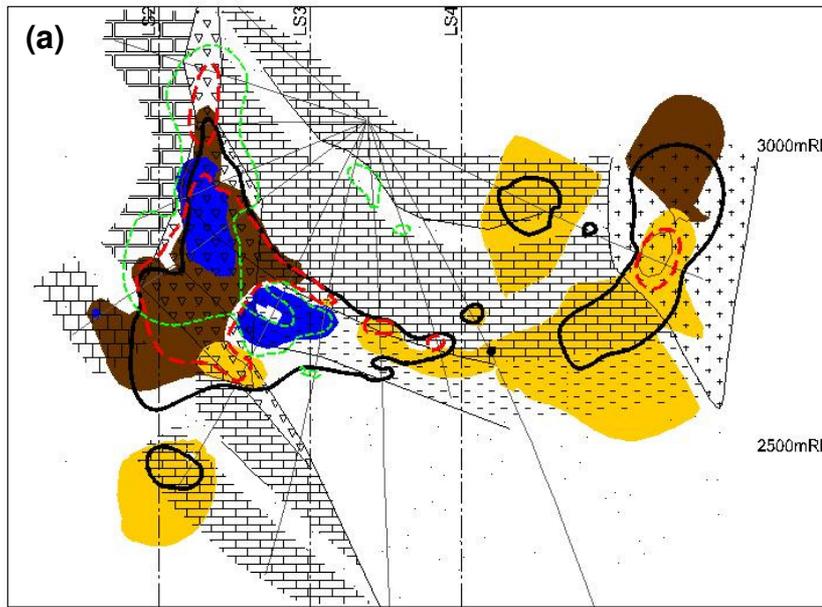

Comparative cross section (a), plan section (b), and long section (c) showing distributions of ore sulphides and Cu-Au-As. The models indicate an association of chalcopyrite-Cu-Au midway between the IFZ and the GIC, covellite-Cu-As in the Kkel adjacent to the IFZ, as well as pyrite-covellite-Cu-Au-As in the upper sections of the IFZ offset. Some areas of Cu-only appear at the margin of the GIC and are related to low intensity pyrite alteration but no logged Cu-sulphide. An Au-As association, which does not correlate with any modeled sulphides may coincide with galena-sphalerite mineralisation at the highest part of the IFZ in the study area.

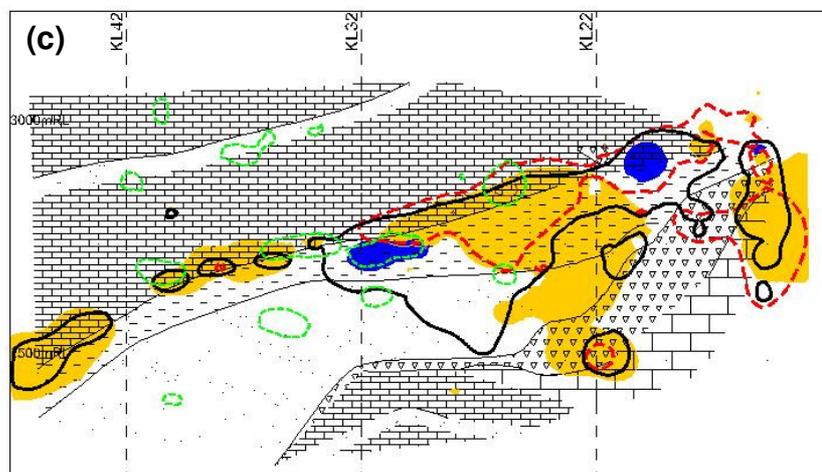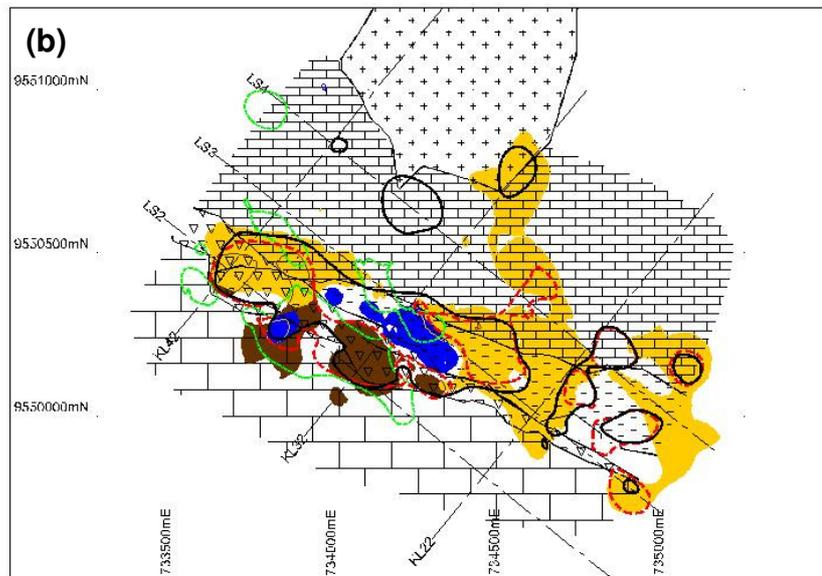

- >30% pyrite
- >2% chalcopyrite
- >2% covellite
- >1% Cu
- >1 g/t Au
- >100ppm As

6 Fluid inclusion studies

This section documents the results of fluid inclusion analysis, including thermometric experiments. Fluid inclusion studies yield data relating to the salinity, temperature of mineral formation and, in some cases, the approximate composition of the fluid. Data were collected from a small population of appropriate samples with the aim of identifying fluid populations.

Samples were initially examined petrographically in order to identify key samples as well as the major fluid inclusion types. The distinction between the different types and generations of fluids preserved in Kucing Liar rock samples was resolved by careful microscopic inspection and documentation of the individual inclusion properties as well as the relationships between fluid inclusions. Suitable samples from as many stages of the paragenesis as possible were identified and prepared for inclusion analysis. Cooling and heating experiments were conducted on small wafers of doubly polished thin sections in order to determine the melting temperatures of ice, the melting temperatures of any salt phases present in the inclusions, and the homogenisation temperature of the vapour bubble with the liquid phase of inclusions. Pieces of 3-5mm diameter were broken from doubly polished thin section wafers, suitable inclusions within the chip were identified and a sketch of each visible inclusion in a single field of view was made documenting each inclusion in terms of type and context. The sizes of vapour bubbles relative to the inclusions (degree of fill) were also recorded.

Empirical and theoretical studies of fluid inclusions have identified relationships between thermometric behaviour and fluid composition. The data are converted to salinity and temperature at entrapment by means of published equations. The different types of fluids involved in the development of Kucing Liar alteration and mineralisation can be identified from these data.

6.1 FLUID INCLUSION PETROGRAPHY

6.1.1 Sample location and descriptions

Fluid inclusions have been identified in diopside, andradite, forsterite, humite, quartz, anhydrite and fluorite, however, only quartz and fluorite were found to contain inclusions large enough to study. Samples were preferentially selected from drill station KL32 as drilling from here presents a cross section through the middle of the known strike extent of mineralisation. Some samples were studied from drillholes on other sections due to their particular high quality and abundance of fluid inclusions (Figure 6-1). As quartz is the main host for fluid inclusions, only Groups II and III of the paragenesis were the major foci of the study, although one sample of fluorite represents the Group IV assemblage directly related to mineralisation. The texture, relative timing and spatial relationships of the fluid inclusion host minerals are described below in order of decreasing elevation.

- KL32-1 236.8m – fluid inclusions hosted in idiomorphic crystals from quartz infill in millimetre and centimetre-scale veins (Plate 6-1a, Plate 6-2a). Pyrite, covellite and enargite have infilled vughs along the middle of the veins. It is unclear if the vein is Group II potassic or Group III silica as it is atypical for both stages. The wall rock is intensely altered by quartz, typical of the later silicification assemblage. The sample comes from the Idenberg fault zone and the original lithology and stratigraphical position are unknown.
- KL32-1 254.7m – fluid inclusions hosted by fluorite infill from vughs that are lined with sub-millimetre crystals of Group III quartz (Plate 6-1b, Plate 6-2b). Covellite and pyrite occur as inclusions in fluorite alongside fluid inclusions. Muscovite infill is present within vughs that are lined with Group III quartz. This muscovite has been used as a geochronology sample (see Chapter 3). The sample is from the centre of the Idenberg fault zone and the original lithology is unidentifiable.

-
- KL48-1 100.2m – fluid inclusions hosted by fragments of coarse-grained quartz crystals (Plate 6-1c, Plate 6-2c). The crystal fragments occur in matrix of covellite, chalcocite and pyrite. The quartz is very similar to that in sample KL32-1 236.8m, and both are believed to most likely be coarse varieties from Group III that occur at higher elevations in the system.
 - KL38-5 224.4m – fluid inclusions hosted in a single millimetre-scale quartz crystal as infill in a vugh surrounded by coeval fine-grained Group III quartz alteration that has replaced penetrative diopside alteration in Waripi limestone (Plate 6-1d, Plate 6-2d).
 - KL32-5 339.2m – fluid inclusions hosted in idiomorphic crystals from millimetre-scale Group III quartz veins (Plate 6-1e, Plate 6-2e). The veins are associated with quartz selvedge alteration that has overprinted K-feldspar-muscovite altered Ekmai limestone. Covellite and pyrite have infilled in vughs adjacent to the grains that host fluid inclusions and occur as spots in the fine-grained quartz alteration.
 - KL32-5 376.4m – fluid inclusions are hosted in idiomorphic crystals from a Group II quartz vein (Plate 6-1f, Plate 6-2f). Bornite and chalcopyrite have infilled vughs in the centre of the vein. The veins are hosted in Ekmai limestone that has separate alteration zones comprising magnetite-calcite-chalcopyrite and K-feldspar-biotite-covellite-chalcocite.
 - KL32-3 354.3m – fluid inclusions hosted in subhedral crystals from centimetre-scale quartz veins (Plate 6-1g, Plate 6-2g, also see Plate 6-4). It is not evident whether the veins developed during Group II potassic alteration or Group III silicification, though they appear to be overprinted by Group III grey quartz alteration. Covellite and minor pyrite infill in fractures and vughs crosscut both the quartz vein and wall rock. The host is unclear but believed to be Ekmai limestone.

- KL32-5 706.7m – fluid inclusions hosted in crystals from centimetre-scale quartz veins and in wall rock quartz grains (Plate 6-1h, Plate 6-2h). The veins are either Group II or Group III. Minor covellite and pyrite occur as spots and fracture infill crosscutting both veins and wall rock alteration. The host rock is the upper Waripi sandstone member.


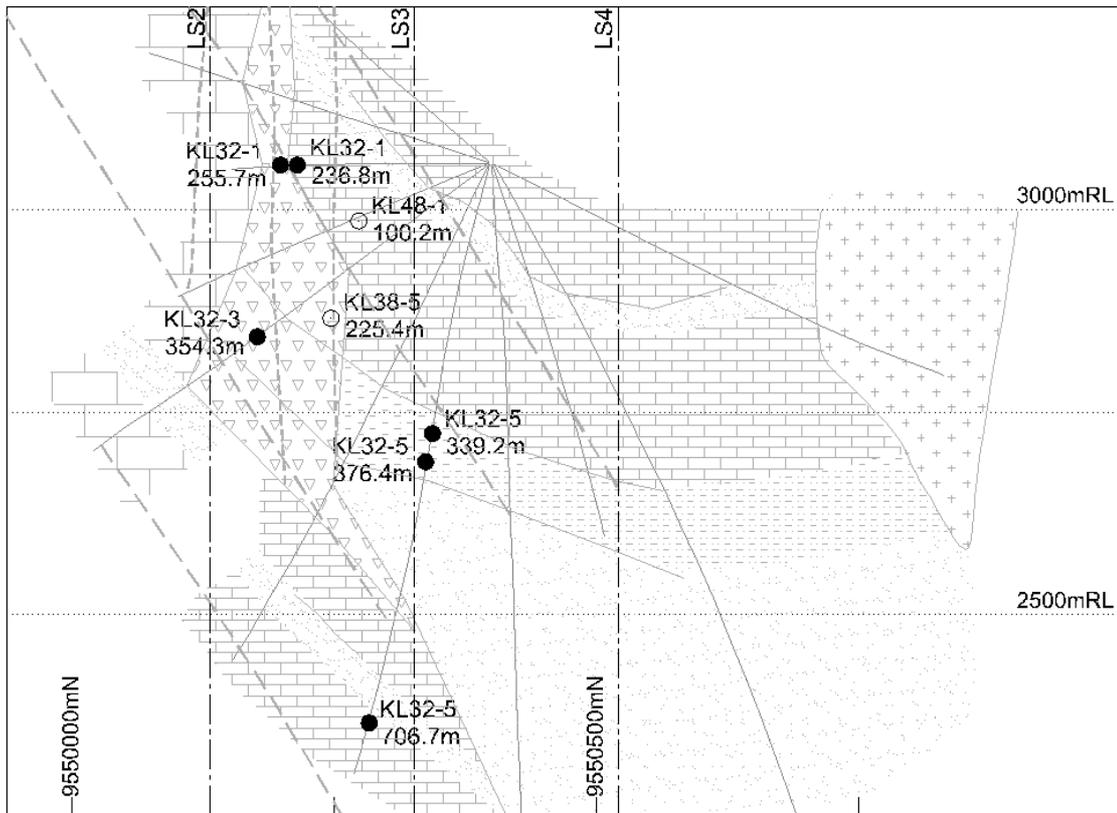


Figure 6-1 Location of fluid inclusion samples


Samples not collected from KL32 drill holes are projected onto section KL32 (see Chapter 3) and marked by an open circle.

Plate 6-1 Photographs of wafers and blocks of fluid inclusion samples

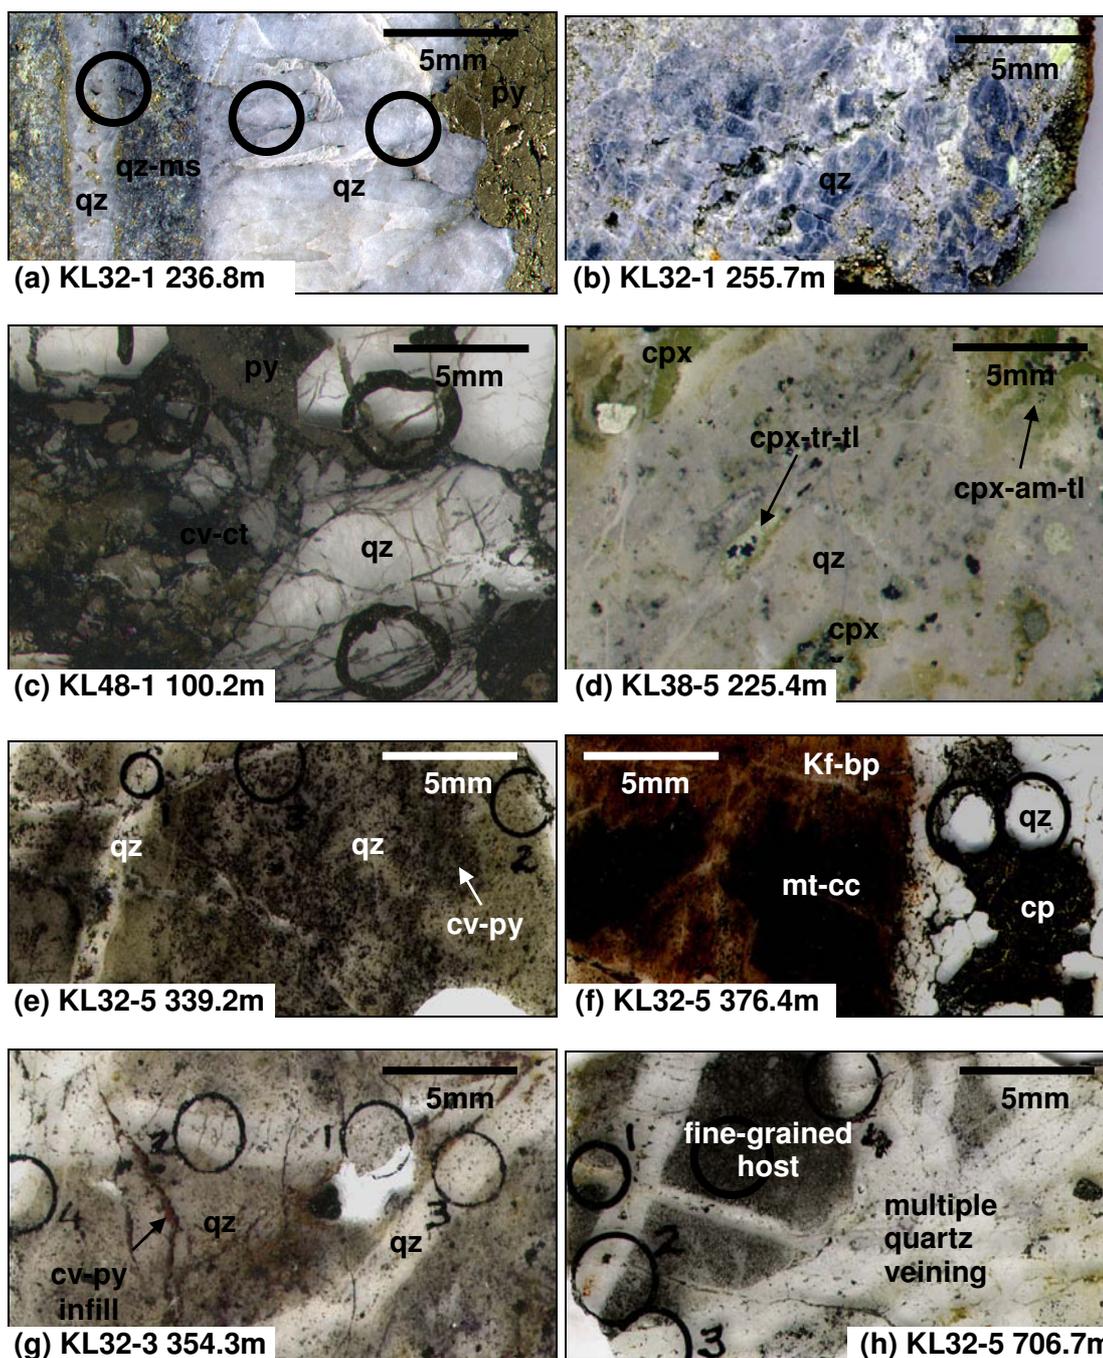

Black circles are drawn around studied fluid inclusion locations. (a) Long quartz crystals protrude into vein centre now filled by coarse pyrite. The quartz is believed to be from Group II and is affected by later quartz-muscovite alteration (b) Fine-grained quartz alteration containing vugs infilled by fluorite and muscovite. (c) Broken quartz crystals in a matrix of pyrite-covellite-chalcocite. The timing of the vein is unknown (d) Fine grained quartz and talc alteration of diopside. (e) Millimetre-scale quartz veins and associated alteration selvages associated with muscovite replacement of feldspar. (f) Potassic-group quartz vein containing pyrite-chalcopyrite-bornite infill. The host rock is K-feldspar + biotite alteration. (g) Quartz veins in quartz alteration crosscut by covellite fracture infill. (h) Crosscutting quartz veins in Group III quartz alteration.

Plate 6-2 Photomicrographs of textural settings of crystals that host fluid inclusions

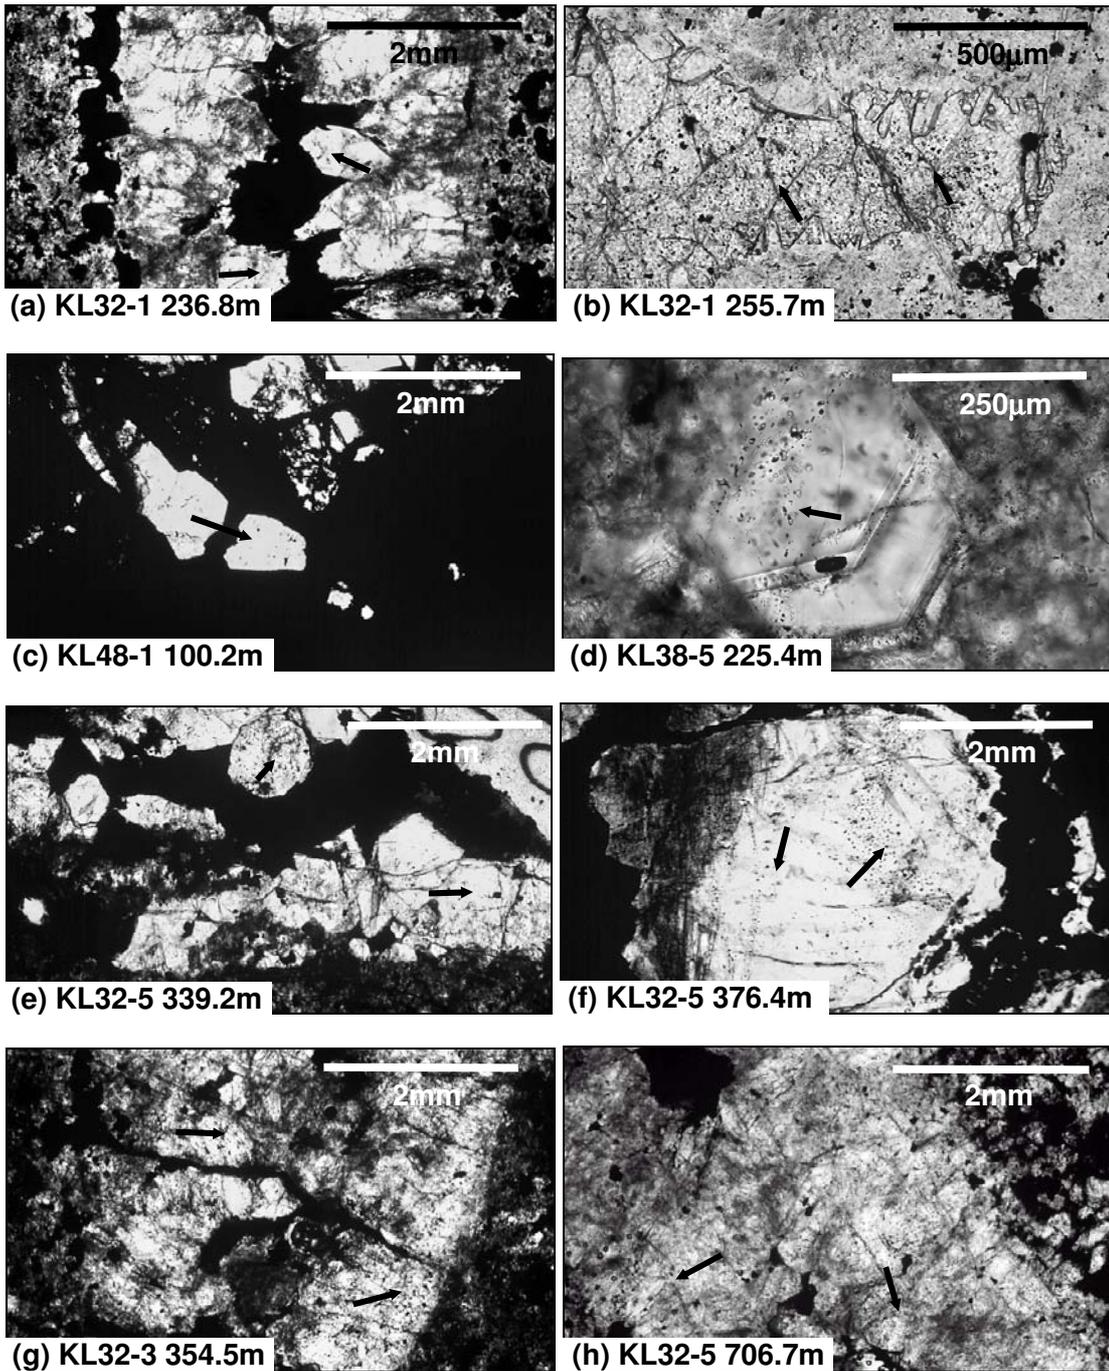

(a) Vein quartz crystals where the host has also been quartz altered host inclusions as crystal growth zones and annealed fractures (b) Fluorite vugh infill lined with quartz crystals in quartz-muscovite altered rock host inclusions as clearly defined trails (c) Fragments of quartz crystals in sulphide matrix contains many large multi-phase inclusions in close proximity to each other (d) A single crystal infilling a vugh in quartz alteration contains inclusions of similar dimension in banded crystal growth (e) Vein quartz crystals adjacent to mineralisation host many different types of inclusions (f) Individual crystal from a quartz vein hosting chalcopyrite-bornite host inclusions in primary growth zones as well as annealed fracture. (g) A variety of fluid inclusion types are hosted in vein quartz crystals in as well as adjacent wall rock alteration. (h) Inclusions are hosted as trails and clusters in quartz stockwork.

6.1.2 Occurrence and paragenesis

There are five principal different types of inclusions distinguishable on the basis of phases present at room temperature. In decreasing order of abundance they are; SLV (solid-liquid-vapour), LV (liquid-vapour), VL (vapour-liquid), V (vapour) and L (liquid) types (Plate 6-3a). SLV inclusions were identified in quartz and diopside only, VL inclusions are only recognised in quartz, and LV inclusions were identified in all minerals containing inclusions. SLV inclusions typically contain a small vapour bubble and at least one solid phase, typically high relief cubic halite commonly accompanied by low relief round sylvite (Plate 6-3b). Hematite is present in some cases as translucent red-coloured chips or idiomorphic hexagonal crystals (Plate 6-1; *cf.* Nash, 1976). SLV inclusions are rounded, equant and six-sided in cross section. The two-phase inclusions that contain only liquid and vapour are designated as either liquid-vapour (LV) or vapour-liquid (VL) type inclusions depending on degree of fill (e.g. Sheppard *et al.*, 1984). Two-phase inclusions (LV and VL) are commonly irregular although significant numbers of VL and LV inclusions are rounded, equant and six-sided in cross section. Idiomorphic inclusions tend to be much smaller than irregular inclusions and of more regular size. SLV inclusions and two-phase inclusions may occur in clusters that display a large range in size. Monophase liquid-only (L) and vapour-only (V) inclusions were not closely scrutinised, as they do not undergo any observable changes during experiments. In one sample (KL32-1 255.7), fluid inclusions were found in close proximity to and seemingly coeval with sulphide inclusions in fluorite including pyrite and covellite.

Fluid inclusions are considered to be primary, pseudosecondary or secondary depending on their mode of occurrence. Primary inclusions form from the same fluid as the surrounding crystal and are recognisable as they commonly are found along planes parallel to the crystal shape (*cf.* Sheppard *et al.*, 1984; Wilkins, 1990). Pseudosecondary inclusions form before the host crystal has annealed so may appear non-parallel to crystal boundaries, but can be distinguished from secondary inclusions as they do not cross crystal boundaries. Secondary inclusions form after the crystal has annealed, implying a separate fluid source to that which the host mineral precipitated

from. Secondary inclusions generally form in distinct fractures which may cross the boundaries between individual host crystals. Fluid inclusions from Kucing Liar samples occur in a variety of settings, including curvilinear trails, random clusters or as isolated inclusions (Plate 6-4). SLV, LV and VL-type inclusions all form trails, though SLV and LV types are the most common. Trails and clusters of SLV and VL inclusions tend to be consistent in size while LV inclusions are more variable. Trails generally comprise a single inclusion type and may be related to growth planes (primary) or visible fractures (secondary) within a crystal (Plate 6-5a, b). SLV inclusions are hosted in regular-shaped voids and tend to be concentrated within the core of crystal shapes and in some examples exhibit layering parallel to crystal boundaries. Clusters of SLV inclusions typically lie in the centre or the apex of quartz crystals (primary or pseudosecondary), whereas the margins of quartz crystals are inclusion free. LV inclusions generally form trails and may be associated with visible fracturing in the crystal, though this is not always the case. The setting of LV inclusions varies from trails constrained within crystal boundaries (pseudosecondary) to less common examples where trails clearly cross crystal boundaries (secondary). LV inclusions are not restricted to fractures and commonly occur as trails that are not continuous across domains within the quartz grain (pseudosecondary) (Plate 6-6b). Large VL inclusions are occasionally hosted in regular voids but do not show any real association with location inside a crystal shape, though they do locally form trails. In many cases it was not always possible to establish primary from pseudosecondary or pseudosecondary from secondary, though secondary was commonly easy to distinguish. SLV inclusions in Kucing Liar are generally primary, related to crystal growth while LV inclusions may be either, primary, pseudosecondary or secondary. SLV and VL inclusion trails are both intersected by fractures which host LV inclusions, indicating the LV-type formed after both SLV and VL-type inclusions. Earlier inclusions are commonly destroyed near the intersection. (Plate 6-6a). LV inclusions were found to be both pseudosecondary and secondary while the VL inclusions may be primary, pseudosecondary or secondary (Plate 6-6a). VL inclusions are the most difficult to assess as they have a number of textural settings and commonly occur as randomly distributed populations (Plate 6-4).

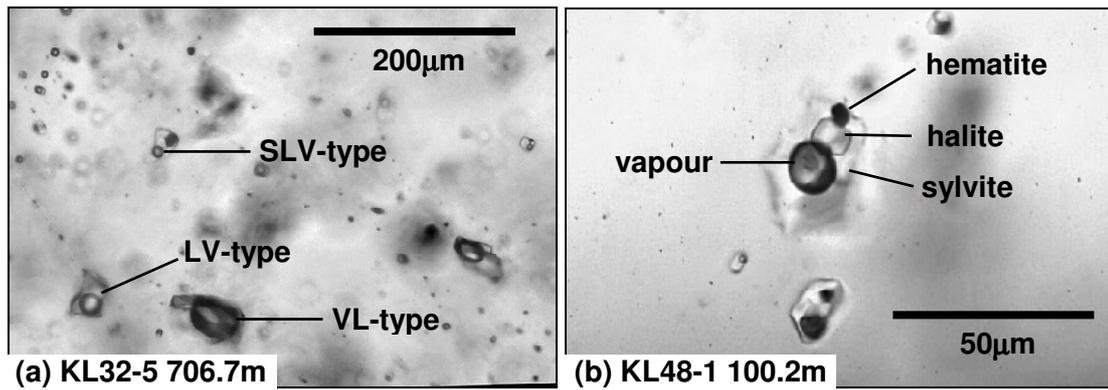


Plate 6-3 Fluid inclusion types in quartz

(a) VL-type inclusions are commonly the largest and occur within irregular or idiomorphic spaces in quartz. LV-type inclusions vary from irregular to regular shapes but are generally not idiomorphic. (b) SLV-type inclusions contain at least one and commonly two salt crystals, a vapour bubble and occasionally, opaque crystals. The low relief of sylvite makes it difficult to observe during melting but the final melt temperature is usually indicated by sudden movement of coexisting phases. Inclusions hosted in quartz.

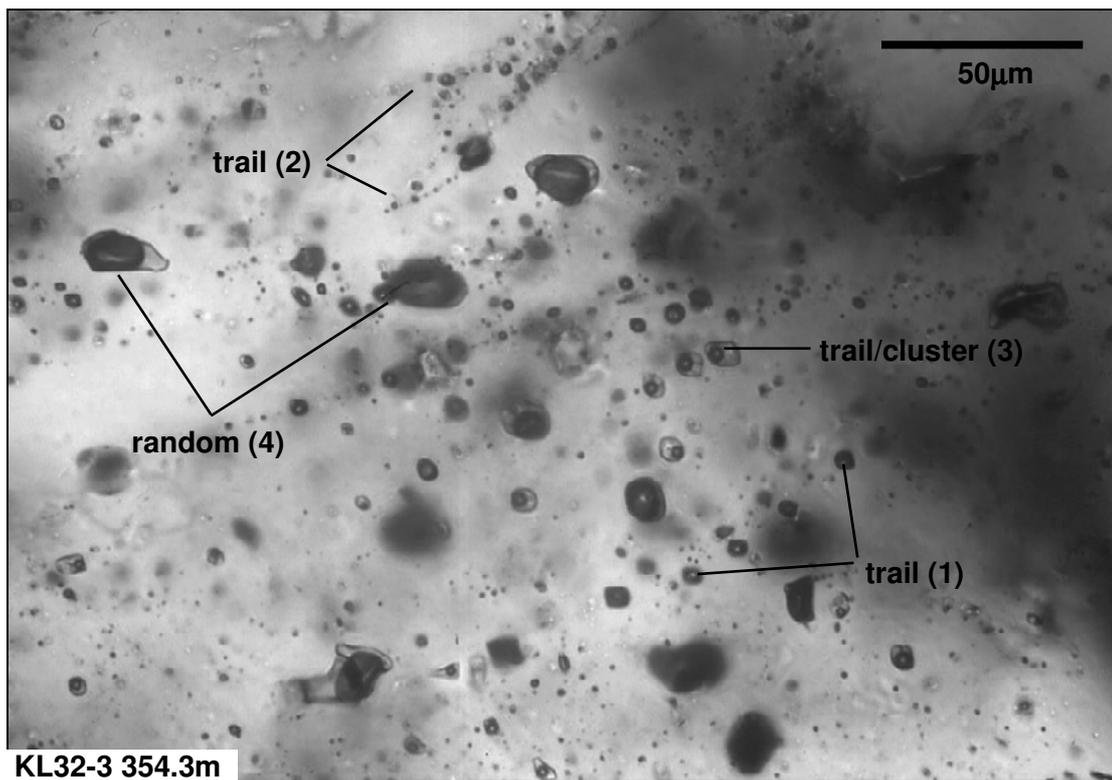


Plate 6-4 Fluid inclusion occurrences in quartz

A photomicrograph of showing possible primary inclusions as trails of uniform-sized VL inclusions (1), pseudosecondary or secondary trails of variable-sized LV inclusions associated with crystal fractures (2), primary or pseudosecondary linear arrays of SLV inclusions (3) and random single VL inclusions that may be primary, pseudosecondary or secondary (4). The parallel nature of SLV and VL trails in examples (1) and (3) suggest formation in a similar setting. While LV trails in (2) are suggestive of overprinting an adjacent VL-type inclusion there are no clear temporal relationships between SLV and VL inclusion trails.

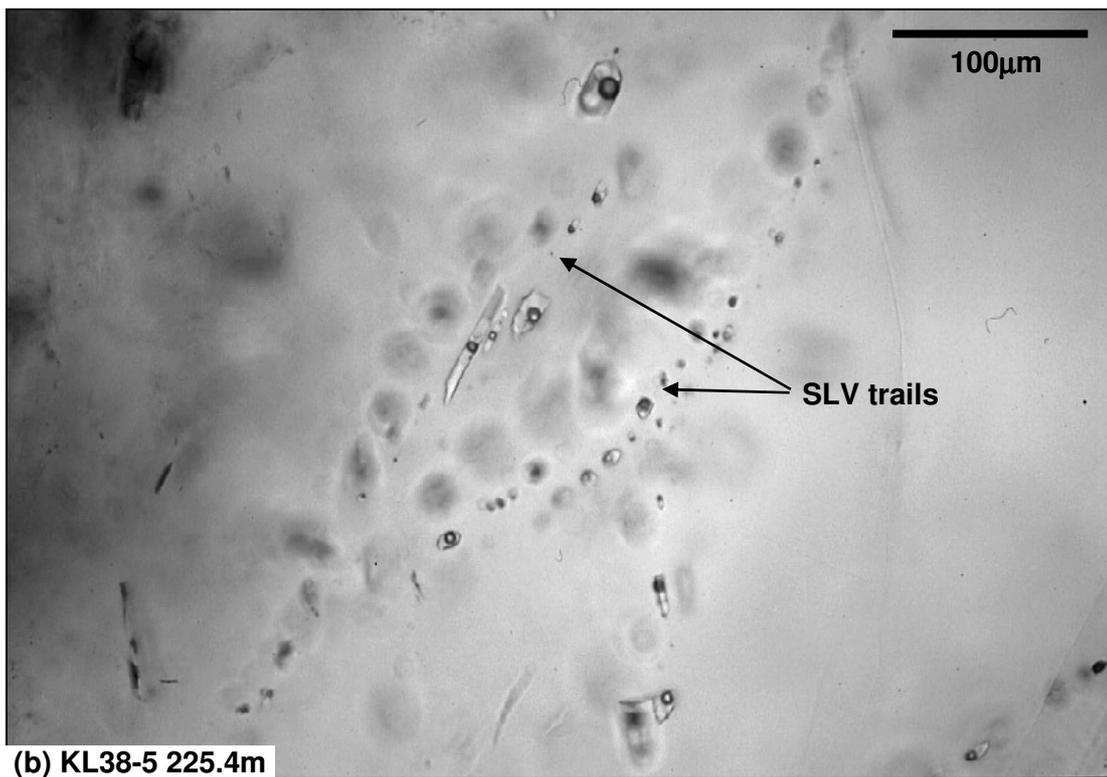
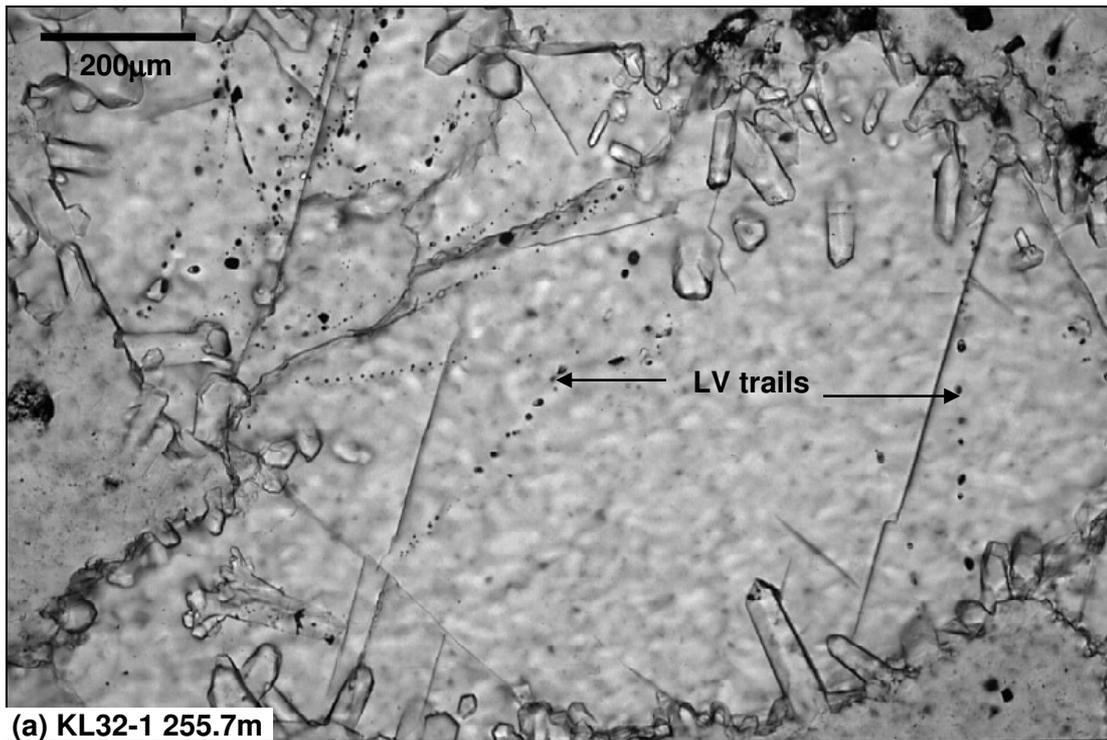


Plate 6-5 Examples of fluid inclusion trails

(a) LV inclusions as single trails across a grain of fluorite. It is unclear if the inclusions are pseudosecondary or secondary. (b) Trails of SLV inclusions in a crystal of quartz. Changing the depth of focus in this sample indicated that single trails form planes through the quartz crystal. The inclusions are considered to be pseudosecondary as they are trapped in curved trails which do not parallel observed crystal faces at low magnification but appear restricted to the quartz grain (see Plate 6-2d).

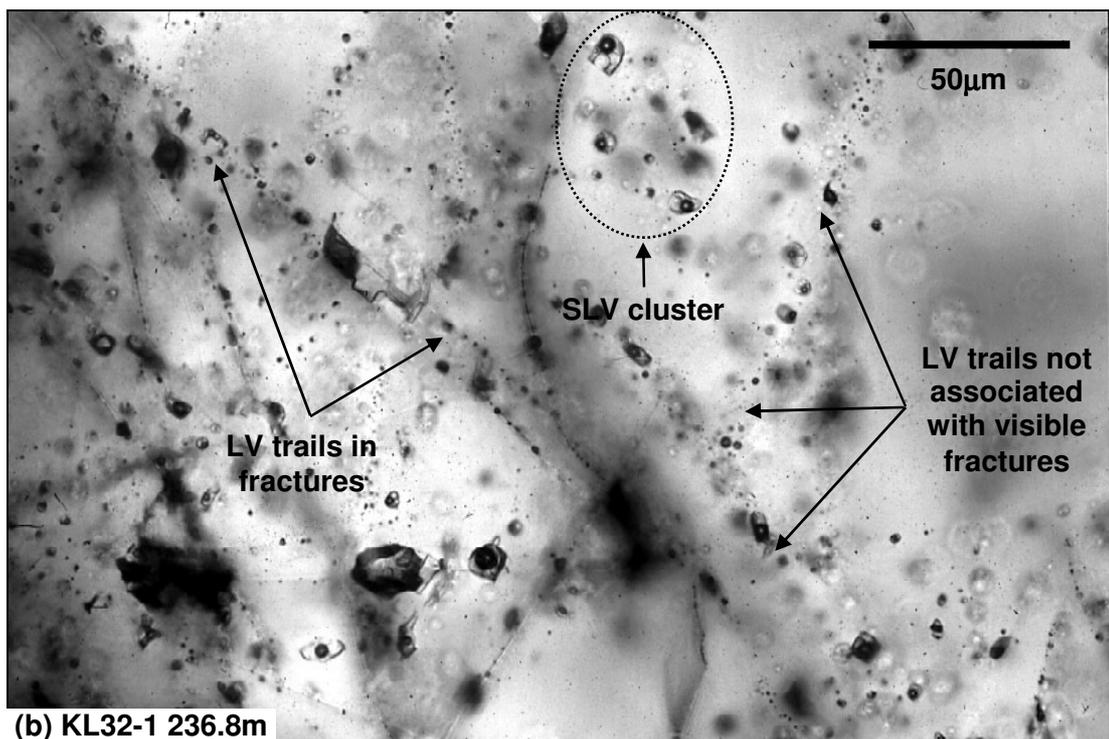
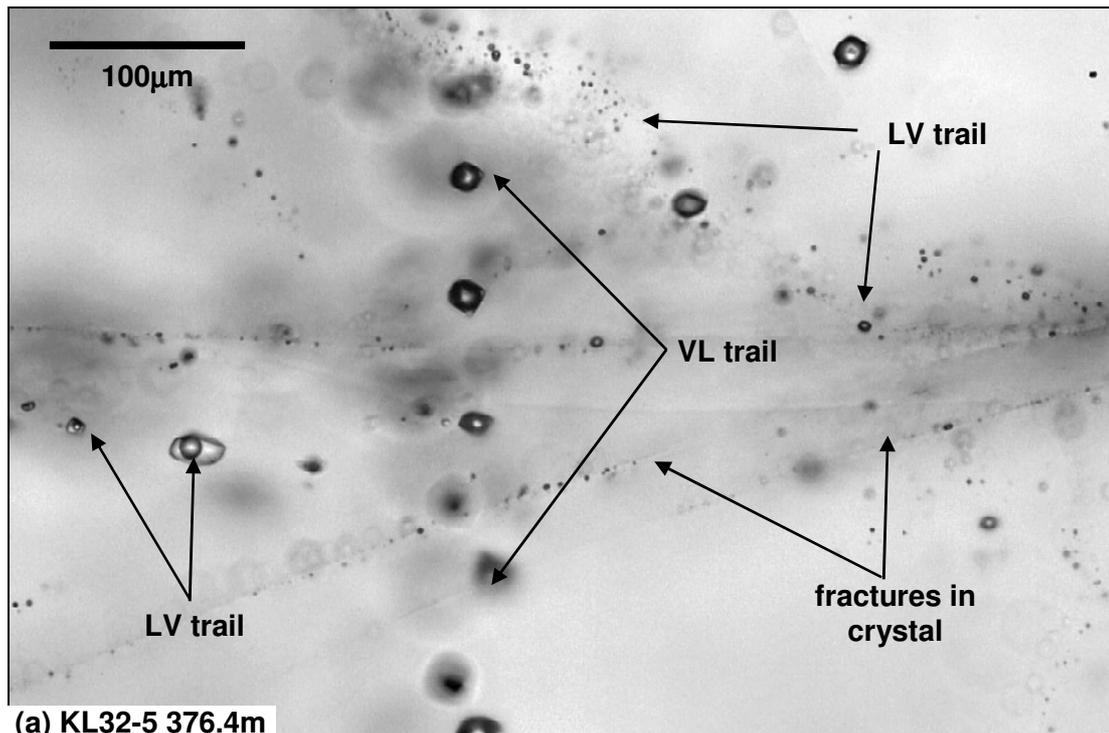


Plate 6-6 Crosscutting fluid inclusion relationships

(a) A trail of LV inclusions that crosscuts trail of VL inclusions in a quartz crystal. The VL inclusions are consistent in size whereas the LV inclusions are highly variable. Both sets of inclusions may represent secondary inclusions, or the earlier VL inclusions may be pseudosecondary. (b) A cluster of variable-sized SLV inclusions (primary or pseudosecondary) is surrounded by variably-sized LV inclusions which are most likely pseudosecondary. Inclusion hosted in clear fractures running top left to centre are either pseudosecondary or secondary and appear to truncate trails of pseudosecondary LV inclusions.

6.2 THERMOMETRIC EXPERIMENTS

The behaviour of the phases within fluid inclusions was observed at 400x magnification and video surveillance in the -200°C to 670°C temperature range (Appendix VI). The chip temperature was monitored to an accuracy of 0.1°C using a slender gauge that also held the chip in place within the sample viewing stage. The temperature of the rock wafer was reduced using gas pumped from a liquid nitrogen vessel and raised by air heated by an electrical element being pumped through the sample stage. The level and rate of heat increase was controlled by a resistance switch. A switch that also cut power to the heating element preserved the temperature at which particular fluid inclusion behaviour was observed. Equipment accuracy of $\pm 2^{\circ}\text{C}$ was established in trial heating experiments on synthetic standards with established homogenisation temperatures of -10.5°C , 190°C & 376.5°C . Freezing experiments were usually conducted prior to heating as a precaution against decrepitation. However, condensation required that apparatus be heated to moderate temperatures ($<250^{\circ}\text{C}$) between multiple freezing behaviour measurements to remove vapour before more freezing experiments could be conducted.

6.2.1 Results of freezing and heating

Various features were investigated including:

- first melting (eutectic temperature) of completely frozen inclusion
- final melting of high relief phases (hydrohalite and antarticite)
- colour and final melting of ice
- final melting of salt phases
- homogenisation of vapour and liquid phases

High relief phase melting, ice melting and vapour-liquid homogenisation temperatures were all difficult to establish for LV-type and VL-type inclusions due to combinations of low visibility and high vapour volumes. Some inclusions hosted in cavities that could not be viewed due to depth of focus were also problematical.

Solid phase melting temperatures

During freezing, 78 of the total 206 inclusions examined turned brown. There were 25 measurements obtained from 14 SLV, 9 LV and 2 VL inclusions for first melting of a non-ice phase, though due to uncertainties in observation and limitations of the equipment the values are only approximate. Thirteen of these eutectic temperatures were measured at or about -52°C , seven between -45 to -49°C , three between -35 to -38°C and two at -26.5°C (Figure 6-2a). In general, SLV inclusions have lower eutectic temperatures than LV and VL inclusions. There were 18 recorded instances where a high relief phase, hydrohalite or antarticite, was identified but only in SLV-type inclusions. The high relief phase hydrohalite was commonly observed to develop in SLV inclusions after first melting but was not consistently identified. Likewise, antarticite, a phase that melts above 0°C , was occasionally recognised in SLV inclusions but not consistently measured. Melting of these high relief phases occurred at different temperatures, which in order of increasing temperature included; nine instances throughout the interval -26 to -34°C , a single instance at -14°C , and six instances between $+10$ and $+50^{\circ}\text{C}$. Distinct populations exist for ice melting (T_{mICE}) observed in LV inclusions. A small group has the lowest (T_{mICE}) between -28 to -24°C and then a steady increase in numbers to a maximum with ice melt temperature between -4 and 0°C (Figure 6-2). The majority of VL inclusions underwent ice melting from -12 to -0°C , and have maxima from -12 and -8°C (Figure 6-2b). Halite (NaCl) melting temperatures were recorded for 71 SLV inclusions, 40 of which also have sylvite (KCl) melting records. Sylvite melt temperatures are generally lower than halite melt temperatures (Figure 6-3a). There is a general correlation of sylvite (T_{mSYLVITE}) and halite (T_{mHALITE}) melting temperatures (Figure 6-3b). The halite melting temperatures are separated into a smaller low temperature (124 - 175°C) and larger high temperature (250 - 450°C) populations (Figure 6-3a). The higher temperature population has an apparent bimodal distribution, the two internal groups distributed symmetrically about maxima at 300 - 325°C and 374 - 400°C (Figure 6-3a).

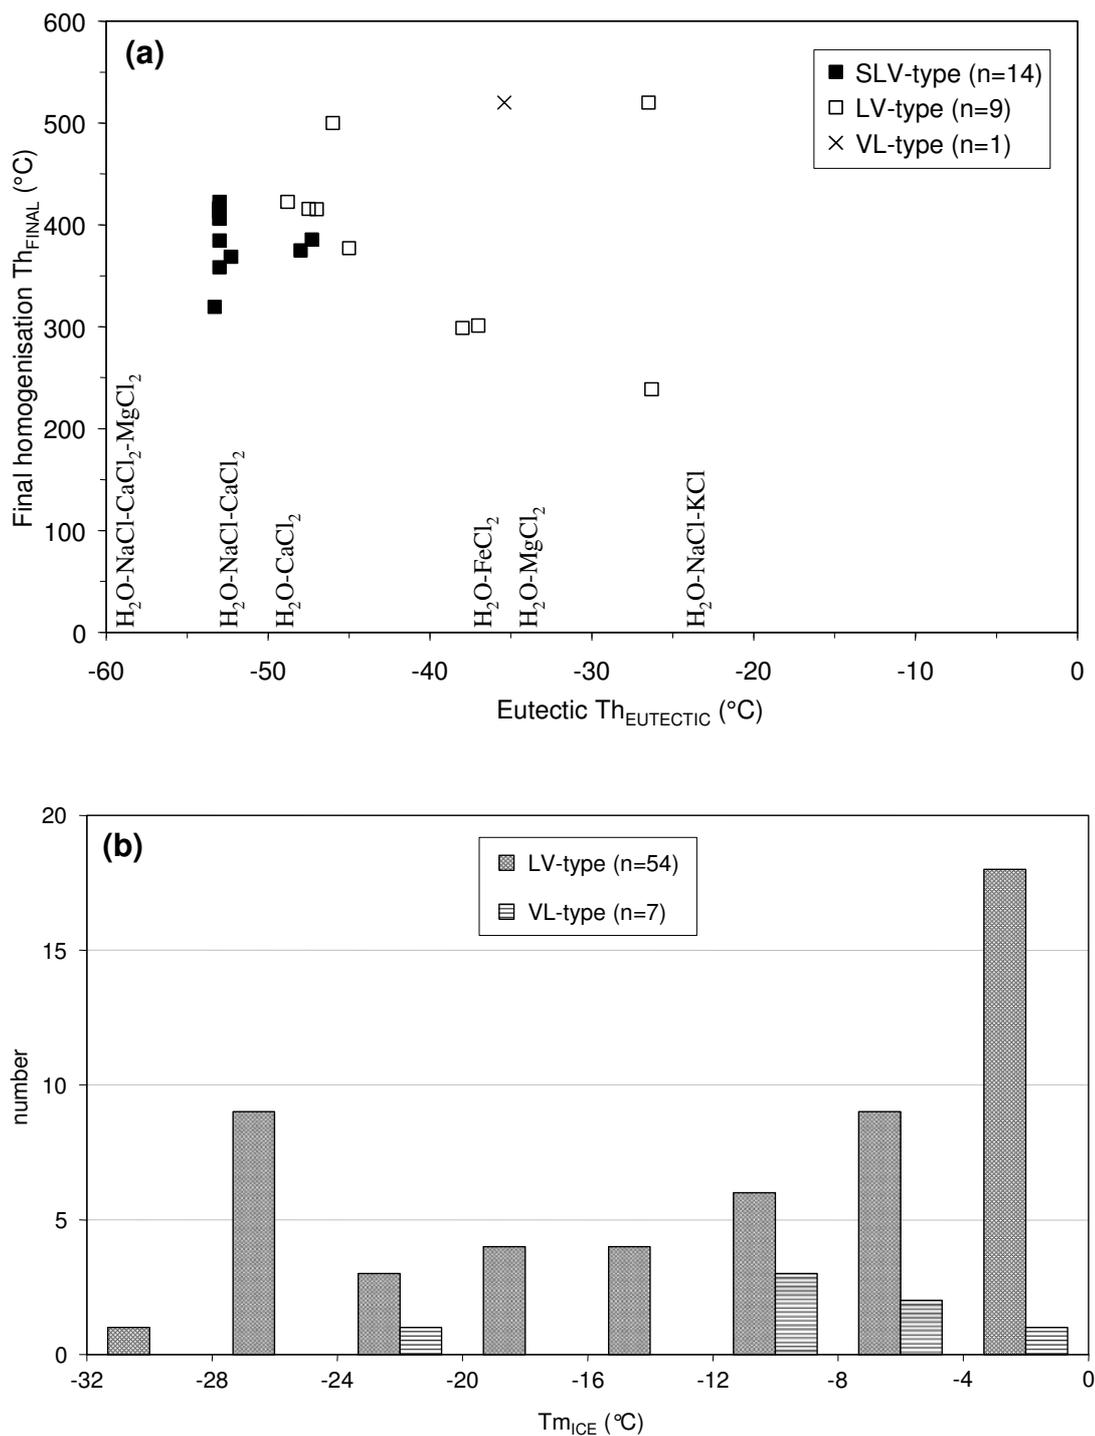


Figure 6-2 First melt (eutectic) and final melting temperatures of ice in frozen inclusions

(a) Eutectic temperatures cluster about $-50^{\circ}C$. These data have uses in determining fluid compositions (see section of fluid compositions). (b) Final ice melting temperatures display a primary maximum near $0^{\circ}C$ as well as a secondary maximum at $-27^{\circ}C$. The bin ranges are plotted along x-axis.

Vapour homogenisation

The vapour phase in an inclusion either homogenises (Th_{VAPOUR}) to liquid ($Th_{(L-V)L}$) or vapour ($Th_{(L-V)V}$). In general, vapour-rich inclusions homogenised to vapour and liquid-rich inclusions homogenised to liquid. As with salt melting, homogenisation occurred gradually, the vapour bubble either became smaller, and vibrated more rapidly with increasing temperature until it disappeared completely, or slowly expanded until the entire inclusion became vapour. Vapour homogenisation, whether to liquid or vapour, was recorded in 194 inclusions. There is a broad trend of increasing vapour homogenisation temperatures with decreasing ice-melting temperatures (Figure 6-4a). There are also indications that there may be more than one fluid represented in individual samples (Figure 6-4).

The majority of SLV-type inclusions have halite melting temperatures similar to or greater than Th_{VAPOUR} , while two smaller populations respectively have low and high halite melting temperatures compared with Th_{VAPOUR} (Figure 6-5). Low halite melting temperatures were observed mainly in a single sample (KL48-2 100.2m), while a group of higher Tm_{HALITE} are derived from inclusions hosted in a number of different samples. Different relationships between halite and vapour occur in cases where Th_{VAPOUR} and Tm_{HALITE} are similar, as exemplified by KL32-1 236.8m and KL32-5 706.7m. In the former Th_{VAPOUR} varies over a large range whereas in KL32-5 706.7m Tm_{HALITE} displays the greater variation (Figure 6-4b). In contrast, the small number of inclusions from KL38-5 224-4m display a consistent relationship of Tm_{HALITE} similar to Th_{VAPOUR} (Figure 6-5).

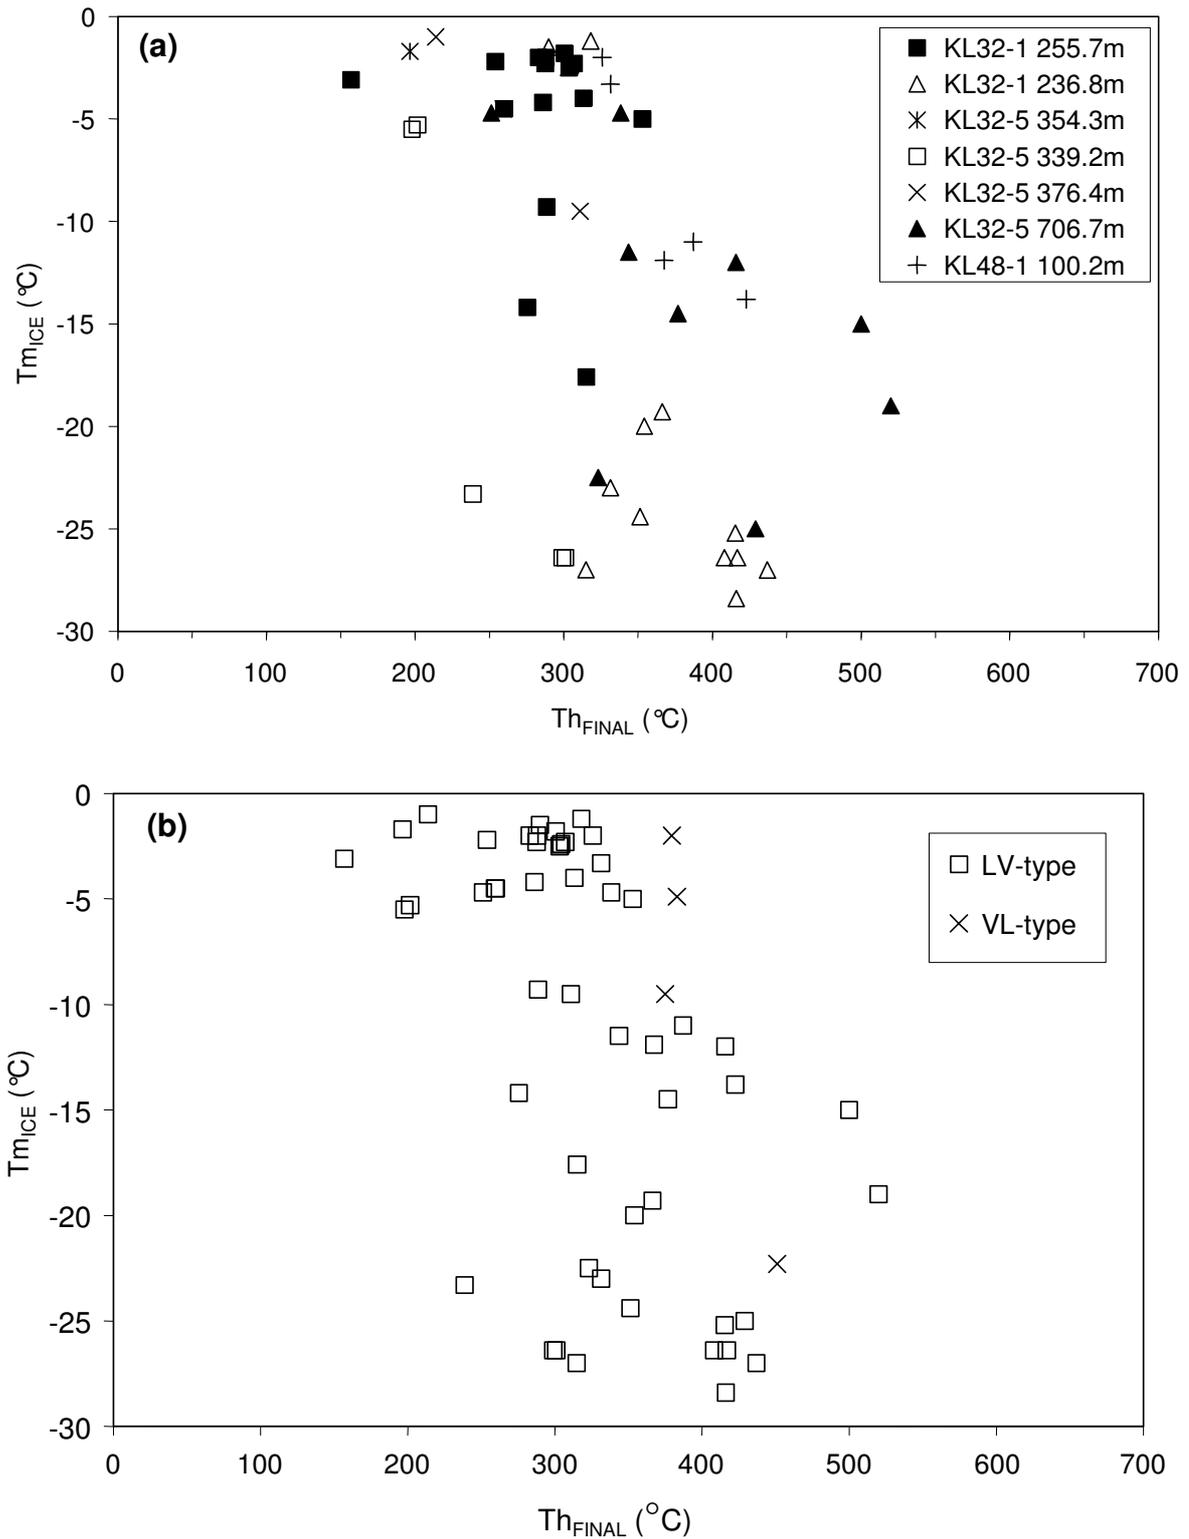


Figure 6-4 Final homogenisation temperature versus ice melting temperatures

(a) The term final homogenisation is used as graph includes LV and VL-type inclusions. A very broad correlation between temperature and ice melting temperature for individual samples is apparent. (b) Only a small number of VL-type inclusions have estimated salinities. LV-type inclusions homogenise to liquid ($T_{h(L-V)L}$), while VL-type inclusions homogenise to vapour ($T_{h(L-V)V}$).

Final homogenisation temperatures (T_{FINAL}), whether to vapour, liquid or salt were recorded in 194 fluid inclusions including 81 SLV, 96 LV and 17 VL inclusions. Final homogenisation temperatures have generally symmetric distributions about discrete maxima (Figure 6-6). Each of these includes different proportions of the three types of inclusions. The low temperature population is represented by LV-type inclusions ($T_{\text{(L-V)L}}$) only and is centred at 174-200°C. The lower of the moderate temperature groups is centred at 300-325°C and dominated by LV-type inclusions ($T_{\text{(L-V)L}}$) but also contains some SLV (T_{VAPOUR} or T_{HALITE}) and VL-type inclusions ($T_{\text{L-V(V)}}$) (Figure 6-6). Conversely, the higher of the moderate temperature groups is centred at 400-425°C dominated by SLV-type inclusions but also contains some LV and VL-type inclusions. The high temperature population include temperatures in excess of 650°C and comprises only VL and SLV-type inclusions. These inclusions had not homogenised at the upper equipment capability limit of 670°C, and so their real homogenisation temperatures may be somewhat higher. These temperatures were mainly derived from SLV inclusions and a single VL inclusion in sample KL32-5 376.4m as well as a single SLV inclusion from KL32-1 236.8m. The inclusions in sample KL32-5 376.4m were of similar appearance (shape, size) and grouped together in trails within an overgrowth on a well-defined quartz crystal. As such these very high measurements are not considered to be due to heterogeneous trapping or necking. Harrison (2000) measured homogenisation temperatures with similarly very high values from inclusions sampled from Grasberg.

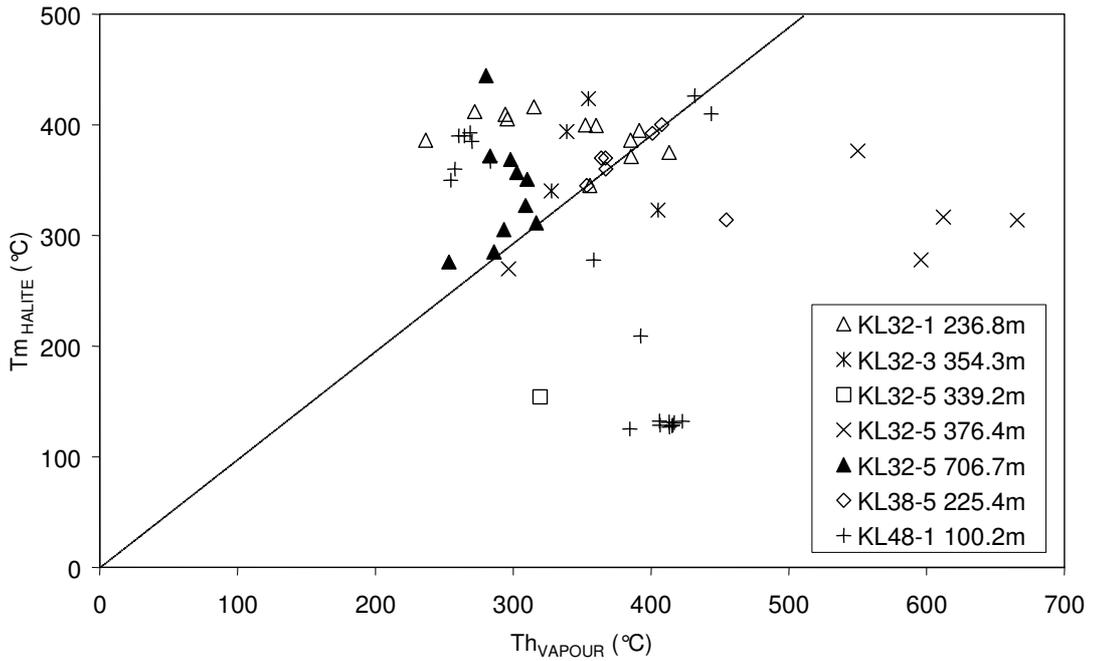


Figure 6-5 Vapour homogenisation versus salt melting temperatures in SLV-type inclusions

A line has been drawn for $Th_{VAPOUR} = Tm_{HALITE}$. It is also apparent that while inclusions from individual samples form clusters, most samples have more than one cluster, possibly indicating the presence of multiple fluids in a single sample

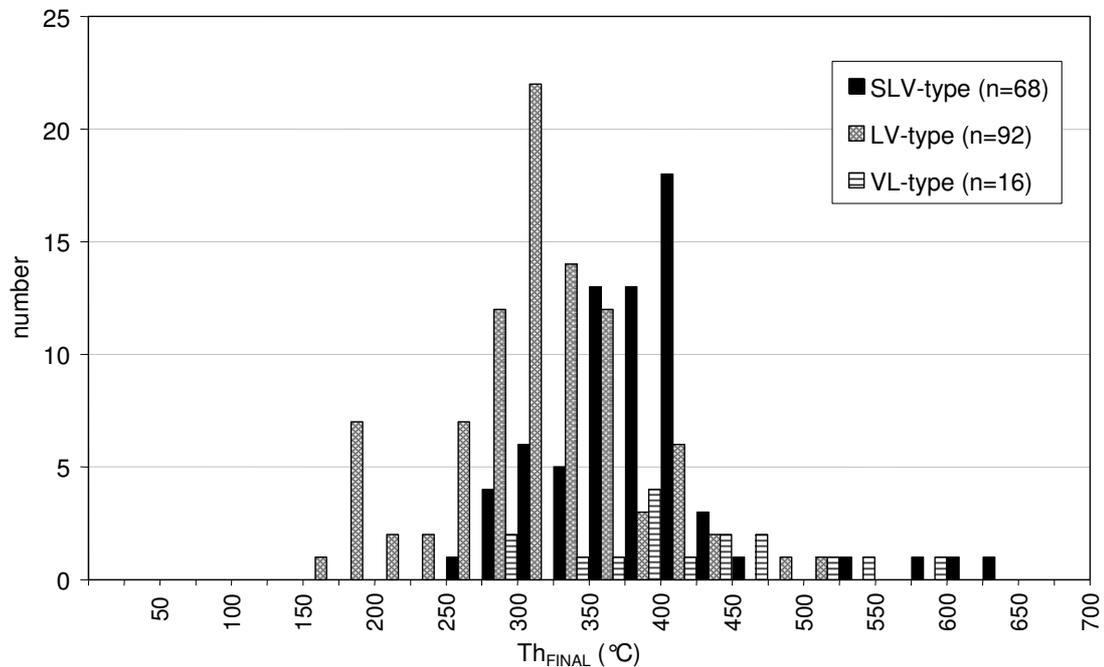


Figure 6-6 Final homogenisation temperatures of fluid inclusions

There were 13 SLV and 5 VL inclusions which did not homogenise at temperatures <650°C. LV-type inclusions homogenise to liquid ($Th_{(L-V)L}$), VL-type inclusions homogenise to vapour ($Th_{(L-V)V}$), while SLV-type inclusions homogenise to liquid either by salt (Tm_{HALITE}) or vapour (Th_{VAPOUR}).

6.2.2 Determination of fluid composition

Salt system

Eutectic temperatures ($T_{m_{EUTECTIC}}$) cluster into groups equivalent to the temperatures for compositions of four different systems. Inclusions with the lowest measured eutectic temperatures have small ranges of $T_{h_{FINAL}}$ but those with higher $T_{m_{EUTECTIC}}$ display a larger range of $T_{h_{FINAL}}$. So, while fluids resembling the systems H_2O -NaCl- $CaCl_2$ and H_2O - $CaCl_2$ have restricted variation of final homogenisation temperatures, those that resemble H_2O - $FeCl_2$ and H_2O -NaCl-KCl systems have a greater range of $T_{h_{FINAL}}$. The change of ice colour to brown is indicative of the presence of calcium as $CaCl_2$ (Brown, 1998). Of the 25 inclusions where a eutectic temperature was measured, 21 were brown ice, suggesting that the fluid inclusions in this group that have H_2O - $FeCl_2$ and H_2O -NaCl-KCl as suggested by $T_{m_{EUTECTIC}}$ also contained $CaCl_2$. The presence of hematite as solid phases in inclusions indicates the presence of abundant Fe in some fluids. Based on the solid phases present in inclusions and melting temperatures of ice, compositions of fluids are most likely to be in the system H_2O -NaCl (\pm KCl \pm $FeCl_2$ \pm $CaCl_2$) (Table 6-1). SLV inclusions generally resemble the system H_2O -NaCl-KCl- $CaCl_2$ while LV inclusions are H_2O -NaCl- $CaCl_2$.

Table 6-1 First melt temperatures of selected water-salt systems

System	Eutectic ($^{\circ}C$)
H_2O -NaCl- $CaCl_2$ - $MgCl_2$	-57
H_2O -NaCl- $CaCl_2$	-52
H_2O - $CaCl_2$	-49.5
H_2O - $FeCl_2$	-35
H_2O - $MgCl_2$	-33.6
H_2O -NaCl-KCl	-23
H_2O -NaCl	-21.2
H_2O -KCl	-10.6

Data reproduced from various sources compiled by Brown (1998).

Salinity calculations

NaCl equivalent fluid inclusion salinities have been calculated from (e.g. Brown, 1998).

$$\text{LV- and VL} \quad (-1.78 * T_m) - (0.0442 * T_m^2) - (0.000557 * T_m^3)$$

$$\text{SLV} \quad 26.242 + (0.4928 * T_d) + (1.42 * T_d^2) - (0.223 * T_d^3) + (0.04129 * T_d^4) + \\ (0.006295 * T_d^5) - (0.001967 * T_d^6) + (0.00011112 * T_d^7)$$

Where T_m = melting temperature of ice and T_d = (halite dissolution temperature) /100. Fluid inclusions from individual samples cluster in terms of their temperature-salinity relationships (Figure 6-7). High salinity inclusions include moderate (250-450°C) and high temperature groups (>600°C). Low salinity inclusions generally have lower T_{FINAL} .

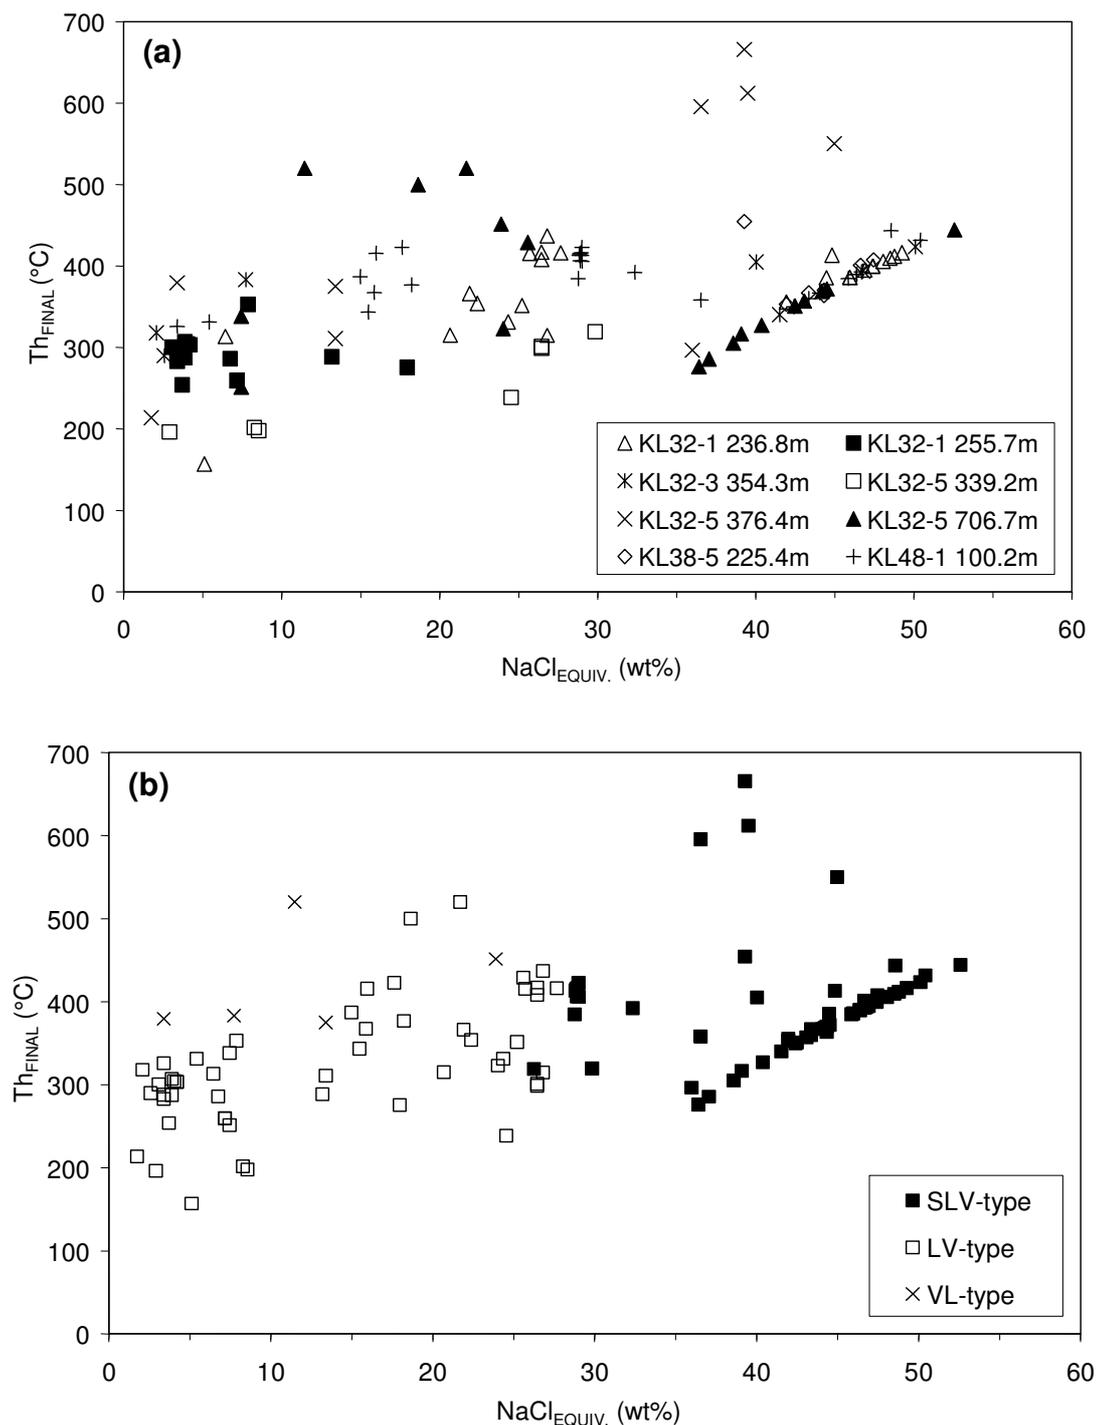


Figure 6-7 Homogenisation temperature versus calculated salinities of fluid inclusions

(a) Results plotted using subdivision by sample. All inclusions are hosted within quartz except for those in sample KL32-1 254-7m which are hosted in fluorite. The linear trend exhibited by the high salinity, moderate temperature group is an artefact of the salinity calculation, and represents inclusions that homogenise by halite dissolution. (b) The same salinity measurements divided by inclusions type (LV, VL and SLV). The term T_{hFINAL} is used as LV-type inclusions homogenise to liquid ($T_{h(L-V)L}$), VL-type inclusions homogenise to vapour ($T_{h(L-V)V}$), while SLV-type inclusions homogenise to liquid either by salt ($T_{hHALITE}$) or vapour ($T_{hVAPOUR}$).

6.3 INTERPRETATION OF FLUID INCLUSION DATA

Experimental data from fluid inclusion analysis indicate that a variety of fluids were involved in the Kucing Liar hydrothermal evolution. The fluids show a distinct populations of high temperature, high salinity brines, more moderate temperatures brines, medium density liquids and finally low density-low salinity water. The last of these is directly related to covellite mineralisation. Low-density phases, characterised as vapour inclusions at room temperature, are found in the same samples and have the same homogenisation temperatures ($T_{h_{V-L(V)}}$) as high and moderate temperature brines ($T_{m_{HALITE}}$ or $T_{h_{VAPOUR}}$). The fluids show little or no graduations between inclusion groupings. The data may suggest temperature shifts and phase changes occurred between the paragenetic stages established in Chapter 3. High temperature fluids are associated with potassic-stage quartz veining while later phyllic-stage quartz alteration host moderate temperature brines (SLV) as well as medium (LV) and low density (VL) phases. While there are no definitive data, many observations point to a phase separation event after silicification which is possibly related to covellite mineralisation.

6.3.1 Fluid populations

Kucing Liar fluids can be divided into discrete populations based on homogenisation temperatures (Figure 6-8a). The data are divided here into four distinct groups; one group (A) having temperatures above 550°C (including many above 670°C), another population at ~420°C (B), a third centred at 300°C (C) and a fourth at 175°C (D). The high temperature group (A) is dominated by brine (SLV) inclusions but also contains a number of vapour (VL) inclusions. The two moderate temperature groups having temperatures around 300°C and ~420°C are more complex and contain variable amounts of all three types of inclusions. Moderate temperature inclusions can be split into two distinct groups based on composition. A higher temperature group at ~420°C (B) is dominated by SLV inclusions while a lower temperature group at ~300°C (C) is dominated by LV inclusions. This second group is associated with covellite mineralisation. The low temperature group (D) is populated by LV-type inclusions only, many of which appeared to

be of secondary origin.

The high and low temperature groups show no real continuity with moderate temperature populations when plotted on a scatter diagram with salinity (Figure 6-7), but there does appear to be a general trend of decreasing temperatures between samples when arranged in a simple plot of inclusion temperatures for each sample (Figure 6-8b). When arranged in this manner it appears that fluids within a single sample exhibit a $\sim 150^{\circ}\text{C}$ temperature range.

6.3.2 Fluid phase development

There are three main types of inclusions found in Kucing Liar samples, namely, SLV (solid-liquid-vapour), LV (liquid-vapour) and VL (vapour-liquid). Hydrothermal fluids derived from magmas may have a range of salinities based on the depth of exsolution (Figure 6-9). Regional and district studies (Chapter 1, Section 1.1.2) of igneous intrusions in the Ertzberg Mining District indicate depth of emplacement as 2km or less. With a pressure of 0.5-1.0 kbar, fluids generated from these magmas will have a salt concentration less than 10 wt.% NaCl (Figure 6-9). Figure 6-9 also indicates that fluids exsolved from magmas up to 1kbar (4km depth) will have gradually increasing salinity after initial water saturation, salinity rising sharply in the last 10% of crystallisation. Note that in much deeper intrusions ($2\text{kb} \approx 8\text{km}$), water saturation occurs at a higher crystallisation point and initial fluids have a very high salinity, while later exsolved fluids have sharply decreasing salinity with increasing crystallisation. For a model of a continuously exsolving fluid to produce the observed fluid types at Kucing Liar would require that the earliest fluids have the lowest salinity and the latest fluids have the highest salinity. While stringent primary, pseudosecondary and secondary distinction has not been possible for Kucing Liar fluid inclusions, general convention where SLV-type inclusions are primary or pseudosecondary while LV-type inclusions are pseudosecondary or secondary. This infers that earliest fluids at Kucing Liar are high density and progress to lower density with time. It is also apparent from thermometric data that SLV-type inclusions are higher temperature than LV-type inclusions. This precludes that the Kucing Liar fluids derived from a continuously exsolving shallowly emplaced

magma.

A second process by which fluids of highly variable salinity may occur together locally is by phase separation, perhaps through the processes of rapid decompression which probably occur when magmatic fluids are released into the surrounding environment (Burnham, 1979). IN this process a rising supercritical fluids intersects its solvus (two-phase field) and separates into high and low density fractions (Figure 6-10). The depth at which this phase separation occurs is dependent upon the temperature of the rising fluid and has an effect of the range in salinity of the resultant high and low density phases (Figure 6-10). The contemporary development of a vapour and brine will develop distinctive fluid inclusion assemblages whereby high and low density type inclusion coexist in a single trail and have similar homogenisation temperatures (e.g. Nash, 1976; Sheppard *et al.*, 1984). Studies of Kucing Liar fluid inclusions do not indicate any instances where this boiling assemblage occurs, however, there are brines and vapours co-existing in samples (see Plate 6-4) that do have similar homogenisation temperatures (Figure 6-4 and also Figure 6-8).

A third and final option is that the various fluid populations are developed from different magmas which underwent fluid saturation at different depths (Figure 6-9). For this model to apply at Kucing Liar, late medium density (LV-type), low salinity fluids would have exsolved from a shallowly emplaced magma overprinting fluids from an early more deeply emplaced intrusion which exsolved high salinity fluids. This process is not discounted though no data has been collected to substantiate depth of emplacement of magmas coeval with Kucing Liar hydrothermal fluids.

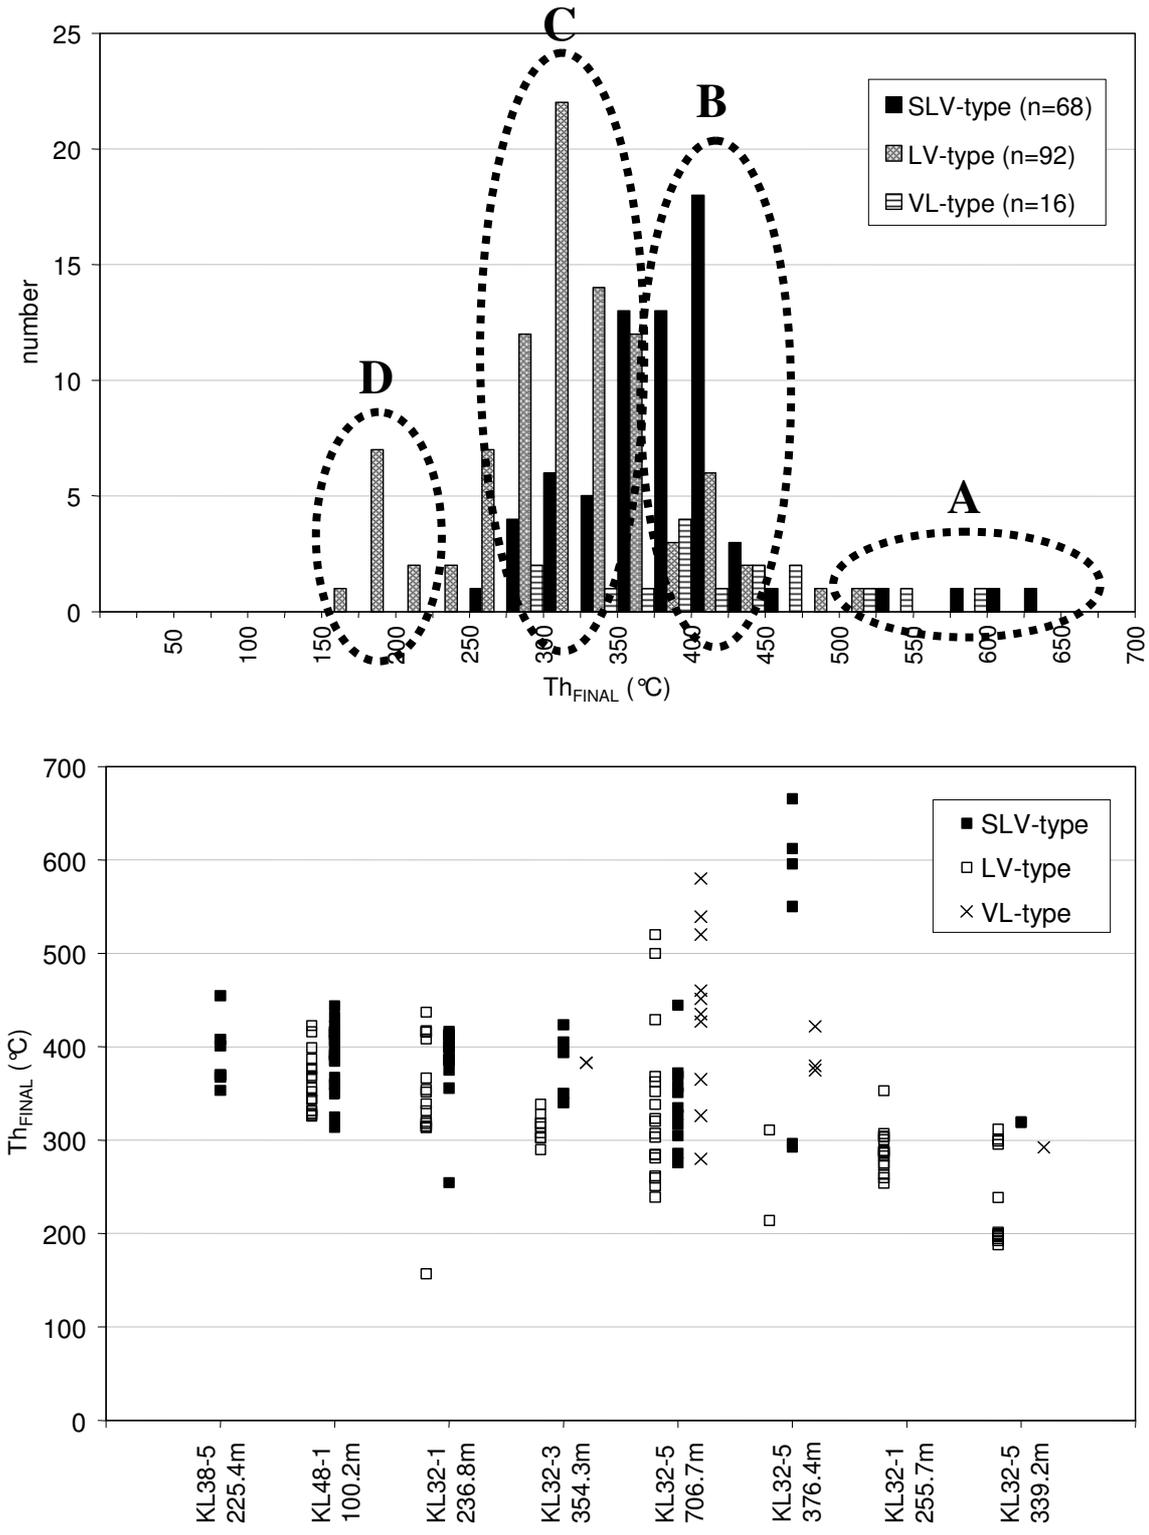


Figure 6-8 Homogenisation temperatures of fluid inclusions

Separation of fluid inclusions into the host samples demonstrates local ranges of homogenisation temperatures. The term Th_{FINAL} is used as LV-type inclusions homogenise to liquid ($Th_{(L-V)L}$), VL-type inclusions homogenise to vapour ($Th_{(L-V)V}$), while SLV-type inclusions homogenise to liquid either by salt (Tm_{HALITE}) or vapour (Th_{VAPOUR}).

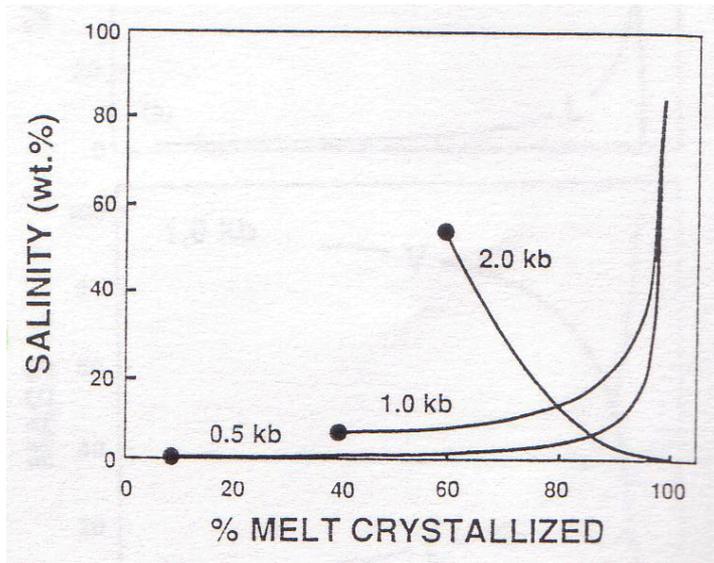


Figure 6-9 Bulk salinity of magmatic fluids exsolved from water saturated magmas

The graph indicates the salinity paths taken by fluid exsolved from magmas at various pressures with increasing crystallisation. The dot represents the point in salinity-crystallisation space at which the magma is saturated with water based on an initial concentration of 2.5 wt.%. Figure reproduced from Cline & Bodnar (1981).

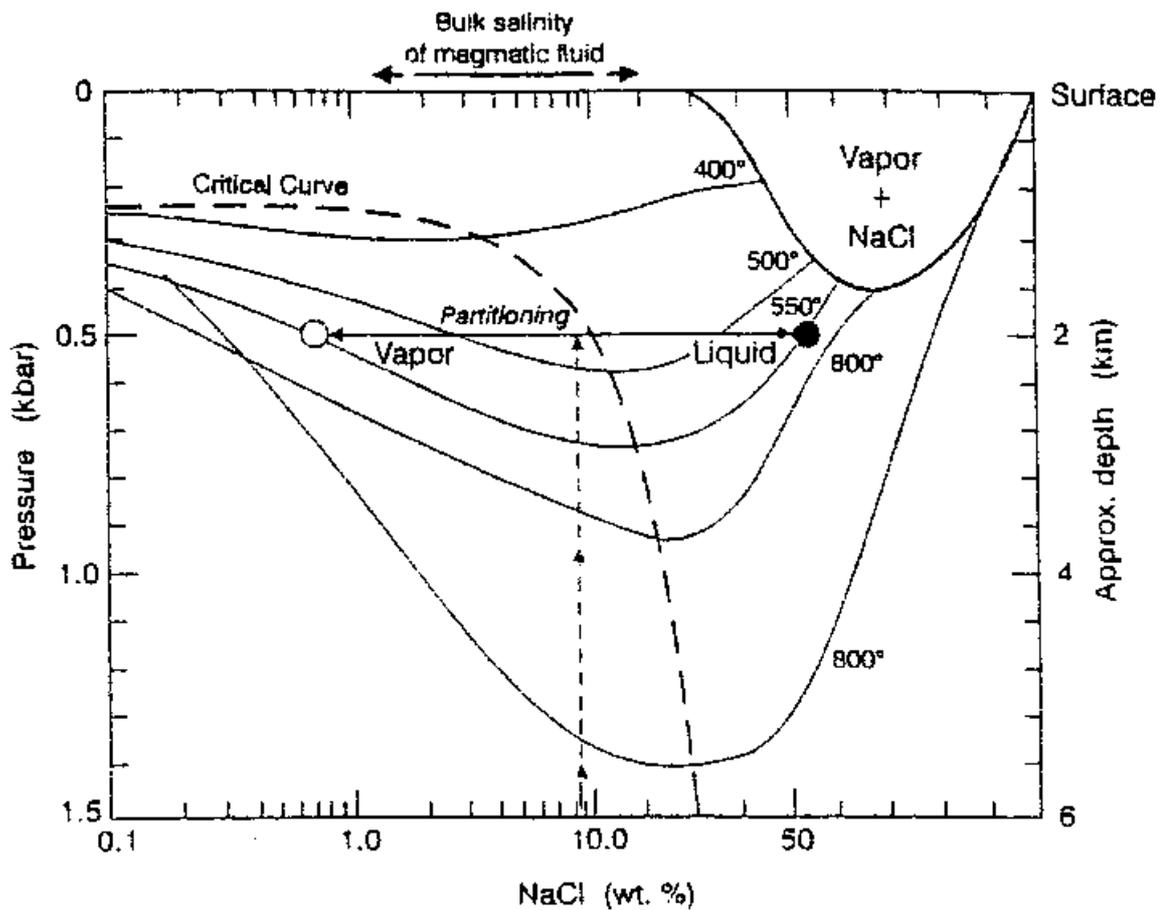


Figure 6-10 Phase separation of critical magmatic fluid (from Meinert, 1998)

The linework indicates that a magmatic fluid of bulk salinity of 8.5wt.%NaCl at 800°C which has cooled to 550°C before ascent can rise to depths equivalent to 0.5kbar before it will undergo separation to high and low density fractions.

7 Stable isotope geochemistry

Stable isotope data place constraints on source reservoir(s) for water in hydrothermal fluids. The data in Chapters 2 and 3 enable these results to be assessed in terms of their temporal and spatial context. This can be used to establish the evolutionary path taken by hydrothermal fluids and the physical processes which occurred during their migration through wall rocks.

Pure mineral samples were collected from as many different minerals and paragenetic assemblages as was available and submitted for isotopic analysis. Individual grains were picked from crushed sample material and separated using a fine brush. Analyses of each sample are converted from mineral to fluid compositions by way of experimentally and theoretically derived fractionation equations for the relevant isotopes in each mineral. This section documents the results of stable isotope analyses for the purposes of determining the sources of hydrothermal waters. Small pieces of rock sample were crushed in hand mortar and pestle until the majority of sample was less than 500 μ m. Individual crystals of each mineral were separated using fine brushes, producing 50 separate samples of 16 mineral phases which were analysed for oxygen isotopes, 13 (6 mineral phases) for hydrogen isotopes, 13 (7 mineral phases) for sulphur isotopes and 3 (2 mineral phases) for carbon isotopes. Oxygen and carbon isotope analyses were submitted to Monash University in Melbourne, Australia, samples for hydrogen analyses were sent to Adrian Boyce at the SUERRC East Kilbride Research Park in Glasgow, Scotland and samples for sulphur analyses sent to Sue Golding at the University of Queensland, Brisbane, Australia. The analytical methods are documented in Appendix VII. The oxygen and hydrogen compositions are reported relative to Standard Mean Ocean Water (V-SMOW). Sulphur is recorded as relative to Cañon Diablo Troilite (CDT). Carbon is reported as relative to calcite from the Peedee Belemnite (PDB). Calculated fluid compositions are then compared to published ranges for primary magmatic water, water derived from metamorphism, and local meteoric water in order to assess the origins of Kucing Liar fluids.

7.1 ISOTOPIC ANALYSES

A total of 63 mineral separates (23 different minerals) from 43 hand specimens were collected (Table 7-1). Most of the samples for stable isotope analysis were collected from a single drill station (KL32) in order to apply consistent spatial context to each sample. Additional samples off this section were dictated by the availability of material or a specific paragenetic association. All minerals except talc, calcite, sphalerite and galena were analysed from more than one sample. A deliberate effort was also made to collect a variety of the modes of development of minerals as documented in Chapter 2 (e.g. pervasive alteration, selvedge alteration of fracture infill). The collection includes samples representing both alteration and infill for single minerals (K-feldspar, biotite, magnetite, anhydrite), plus analyses of the same phase from different host units and lithology. Multiple pure samples of various minerals from each paragenetic stage were collected for oxygen isotope analysis. Only six hydroxyl-bearing minerals were analysed for hydrogen isotope composition. For green phlogopite, muscovite and serpentine only one sample was used. Nevertheless, each Group of the paragenesis is represented by at least one hydrogen isotope analysis (Table 7-1). Only Groups II and III have been assessed for sulphur isotope composition via pure samples of anhydrite, pyrite, chalcopyrite and covellite. A variety of styles of anhydrite and pyrite occurrence were sampled but only two samples each of chalcopyrite and covellite are included.

7.1.1 Results of analyses

Multiple analyses of individual mineral phases define single populations of $\delta^{18}\text{O}$ spread over narrow ranges of 2-3‰ except for K-feldspar, tremolite, anhydrite, which are bimodal, and quartz alteration which has a large range of $\delta^{18}\text{O}$ (6-12‰). Most $\delta^{18}\text{O}_{\text{MINERAL}}$ values lie between 0 and 12‰, with only dolomite samples having outlying values at 22‰ (Figure 7-1). Earlier formed minerals display narrower ranges of $\delta^{18}\text{O}$ than later formed minerals (Figure 7-1a). Skarn and potassic minerals (diopside, garnet and humite as well as biotite and quartz veins) all display narrow ranges of 1-3‰. Two samples of K-feldspar have quite different values. Magnetite has a

slightly broader range of 4‰ while tremolite-actinolite values are divided into 3-4‰ and 7-8‰ (Table 7-1). δD ranges between -275 and -100‰, with an apparent mode between -150 and -175‰ (Figure 7-1b). Two humite samples display a large difference in δD , with the single green phlogopite sample lying between them. Three biotite samples have a narrow range of δD from -180 to -200 (Table 7-1). $\delta^{34}S$ values form two populations, respectively comprising sulphate and sulphide species (Figure 7-1c). Anhydrite samples have a narrower range of $\delta^{34}S$ (2‰) relative to $\delta^{18}O$ (3.5‰) for the same samples (Table 7-1). The six samples of pyrite have a large but continuous range of $\delta^{34}S$ between -8 and 2‰. The lowest of these (-6.2‰), is from a sample of fine pyrite, whereas $\delta^{34}S$ in coarse pyrite from the same sample is -4‰ and similar to other samples of coarse pyrite (Table 7-1). Only three samples of chalcopyrite and two of covellite were analysed and have very different values of $\delta^{34}S$, within the same range as pyrite. Galena and sphalerite have similar $\delta^{34}S$ equivalent to the highest pyrite and chalcopyrite values.

Lithology is not a significant factor in the isotopic composition of hydrothermal minerals. Diopside samples collected from shale and limestone wall rocks have identical oxygen compositions, as do biotite samples from shale and fault zone and quartz veins hosted by shale, sandstone and fault zones (Table 7-1). Similarly, although quartz alteration samples have a wider range of compositions than skarn minerals, the variation is not related to wall rock lithology. Limited data from K-feldspar might suggest some lithological control though the data are limited to two samples (Table 7-1). Textural variations in mineral development have a minor effect on mineral compositions where some minerals display variability in isotope chemistry that may be related to mode of occurrence. For example, anhydrite $\delta^{18}O$ values for alteration are significantly higher (2.8 and 4.8‰) than infill (1.2‰) (Table 7-1). However, there appears to be no textural characteristic (grainsize or colour) or growth form (infill or alteration) of tremolite-actinolite that is coincident with the variable $\delta^{18}O$, nor a single textural characteristic that parallels the large range of $\delta^{18}O$ of quartz alteration.

Table 7-1 Stable isotope samples and results (‰)

Drill hole	Depth	Lith	Mineral	Form	Group	$\delta^{18}\text{O}$	δD	$\delta^{34}\text{S}$	$\delta^{13}\text{C}$
KLS3-1	1420.7	lst	dolomite	Alt	Host	22.0			1.3
KL38-05	814.1	lst	dolomite	Alt	Host	22.5			2.5
KL32-03	388.3	shl	diopside	Alt	I	4-4			
KL32-09	342.9	lst	diopside	Alt	I	4-8			
KL32-04	247.5	lst	diopside	Alt	I	6.0			
KL32-07	394.5	shl	diopside	Alt	I	6.1			
KL38-05	708.2	lst	diopside	Alt	I	6.5			
KL26-08	384-4	shl	garnet (green)	Alt	I	4.1			
KL32-03	381.5	shl	garnet (green)	Alt	I	4.2			
KL26-08	384-4	shl	garnet (red)	Alt	I	4.5			
KL16-09	57.2	lst	humite	Alt	I	3.0	-257		
KL26-08	318.0	lst	humite	Alt	I	3.3	-168		
KL28-01	360.3	unk	green phlogopite	Alt	I	6.1	-217		
KL32-08	331.0	lst	green phlogopite	Alt	I	7.0			
KL28-01	360.3	unk	K-feldspar	Inf	II	8.0			
KL38-05	711.5	shl	K-feldspar	Alt	II	12.0			
KL32-07	601.0	sst	quartz (vein)	Inf	II	10.4			
KL32-08	480.1	shl	quartz (vein)	Inf	II	10.5			
KL32-01	263.8	unk	quartz (vein)	Inf	II	11.4			
KL32-07	349.5	shl	quartz (vein)	Inf	II	11.5			
KL32-07	342.2	lst	magnetite	Alt	II	0.9			
KL28-01	272.9	lst	magnetite	Alt	II	1.3			
KL32-03	416.9	unk	magnetite	Alt	II	1.6			
KL32-05	313.9	lst	magnetite	Alt	II	2.6			
KL32-07	349.5	shl	magnetite	Inf	II	3.1			
KL20-09	464-3	shl	biotite	Inf	II	3.4	-195		
KL32-05	652.4	shl	biotite	Inf	II	4.0	-204		
KL32-05	539.6	unk	biotite	Alt	II	4.3	-181		
KL32-08	410.0	lst	serpentine	Alt	III	6.1			
KL32-08	331.0	lst	serpentine	Alt	III	6.2	-154		
KL32-05	539.6	unk	tremolite	Alt	II	3.2	-181		
KL32-04	500.8	lst	tremolite	Alt	II	3.4	-110		
KL32-08	357.1	lst	tremolite	Alt	II	3.4	-154		
KL38-05	638.9	lst	tremolite	Alt	II	7.0			
KL28-01	266.9	lst	tremolite	Alt	II	7.9	-159		
KL32-07	329.0	lst	talc	Alt	III	4.9			

Hole	Depth	Lith	Mineral	Form	Group	$\delta^{18}\text{O}$	δD	$\delta^{34}\text{S}$	$\delta^{13}\text{C}$
KL32-07	342.2	lst	anhydrite	Inf	III	1.2		11.6	
KL32-08	410.0	lst	anhydrite	Alt	III	2.8		9.5	
KL32-08	480.1	shl	anhydrite	Alt	III	4.8		10.2	
KL32-03	416.9	unk	anhydrite	Inf	III	1.2		10.7	
KL38-05	224-4	lst	quartz (alt)	Alt	III	6.3			
KL32-05	339.2	shl	quartz (alt)	Alt	III	7.1			
KL30-01	222.1	lst	quartz (alt)	Alt	III	8.4			
KL32-03	354.3	shl	quartz (alt)	Alt	III	9.9			
KL32-05	296.3	lst	quartz (alt)	Alt	III	10.0			
KL32-05	706.7	sst	quartz (alt)	Alt	III	11.0			
KL32-01	254-7	unk	quartz (alt)	Alt	III	11.3			
KL32-01	254-7	unk	muscovite	Inf	III	6.2			
KL32-08	454-9	shl	muscovite	Alt	III	6.9	-105		
KL32-03	426.6	unk	calcite	Inf	IV	9.3			0.4
KL32-05	539.6	unk	chalcopryrite	Inf	IV			-3.8	
KL32-03	416.9	unk	chalcopryrite	Inf	IV			-2.9	
KL28-01	266.9	lst	chalcopryrite	Alt	IV			2.4	
KL28-01	266.9	lst	pyrite	Alt	IV			-2.0	
KL32-05	539.6	unk	pyrite	Inf	IV			-3.1	
KL32-03	426.6	unk	pyrite (fine)	Alt	IV			-6.2	
KL32-03	426.6	unk	pyrite (coarse)	Alt	IV			-4.0	
KL32-08	454-9	shl	pyrite (coarse)	Inf	IV			-2.7	
KL32-01	254-7	unk	pyrite (coarse)	Alt	IV			0.1	
KL20-05	237.8	lst	covellite	Inf	IV			-6.1	
KL42-02	100.2	sst	covellite	Inf	IV			-0.1	
KL42-05	337.0	lst	galena	Inf	IV			1.3	
KL42-05	337.0	lst	sphalerite	Inf	IV			2.4	

Table 7-1 Stable isotope samples and results (cont.)

Abbreviations: *lst* = limestone, *shl* = shale, *sst* = sandstone, *unk* = unknown; *Alt* = alteration, *Inf* = infill. The measured isotope ratios are calculated as a shift from zero (δ) reported in permil (‰) deviation from standard (V-SMOW for oxygen and hydrogen, CDT for sulphur and V-PDB for carbon). Analytical precision is $\pm 0.2\%$ in silicates and $\pm 0.1\%$ in carbonates in for oxygen, $\pm 2\%$ for hydrogen and $\pm 0.3\%$ for sulphur.

7.1.2 Fluid compositions

The isotopic fractionation between a mineral and a coexisting fluid is calculated by determining the difference (Δ) in isotopic compositions (δ) of the mineral (substance) and water thus (e.g.):

$$\Delta^{18}\text{O}_{\text{MINERAL-FLUID}} = \delta^{18}\text{O}_{\text{MINERAL}} - \delta^{18}\text{O}_{\text{FLUID}}$$

For the selected minerals from Kucing Liar, the value of Δ is calculated for ^{18}O , D, and ^{34}S from the equations listed in Table 7-3, Table 7-4 and Table 7-5 which allow for the calculation of the isotopic composition of fluids. Calculation of Δ values requires the temperature of mineral formation for input into the equilibrium equations. Estimated temperatures of formation for each mineral are listed in Table 7-2 and are based on constraints from phase equilibria (Group I, II and III) and fluid inclusion homogenisation temperatures (Group II and III). While the temperatures may be broad estimates only, the slope of the curves in the vicinity of the temperatures are so slight that in many cases a difference between assumed and real temperatures of $\pm 100^\circ\text{C}$ will only result in a change of calculated $\Delta_{\text{MINERAL-FLUID}}$ of $\pm 2\%$ and not greater than $\pm 5\%$ in the most extreme cases (dolomite, anhydrite, serpentine, talc, calcite).

Table 7-2 Temperatures used for calculating fluid isotope compositions

Mineral	Estimated T (°C)
Dolomite: $\text{CaMg}(\text{CO}_3)_2$	300
Diopside: $\text{CaMgSi}_2\text{O}_6$	650
Andradite: $\text{Ca}_3\text{Fe}_2\text{Si}_3\text{O}_{12}$	650
Grossular: $\text{Ca}_3\text{Al}_2\text{Si}_3\text{O}_{12}$	650
Humite: $(\text{Mg,Fe})_7(\text{SiO}_4)_3(\text{F,OH})_2$	650
Phlogopite-OH: $\text{KMg}_3\text{AlSi}_3\text{O}_{10}(\text{OH})_2$	550
K-feldspar: KAlSi_3O_8	550
Quartz veins: SiO_2	700
Magnetite: Fe_3O_4	450
Biotite: $\text{K}(\text{Mg,Fe})_3(\text{Si}_3\text{Al})\text{O}_{10}(\text{OH,F})_2$	550
Tremolite: $\text{Ca}_2\text{Mg}_5\text{Si}_8\text{O}_{22}(\text{OH})_2$	450
Serpentine: $\text{Mg}_3\text{Si}_2\text{O}_5(\text{OH})_4$	350
Anhydrite: CaSO_4	400
Quartz alteration: SiO_2	350
Muscovite: $\text{KAl}_3\text{Si}_3\text{O}_{10}(\text{OH})_2$	350
Talc: $\text{Mg}_3\text{Si}_4\text{O}_{10}(\text{OH})_2$	350
Calcite: CaCO_3	350
Pyrite: FeS_2	350
Chalcopyrite: CuFeS_2	350
Covellite: CuS	350
Sphalerite: ZnS	300
Galena: PbS	300

Temperatures for quartz veins and quartz alteration are based on directly measured homogenisation temperatures for fluid inclusions while covellite is assumed from measurement of paragenetically associated fluorite-hosted inclusions (see Chapter 6). All other temperatures are based on either paragenetic associations or published information for similar styles of alteration in skarn deposits. The assumed temperatures for all other of the minerals either lie on a low slope section of the fractionation curve or are well constrained such that the amount of error introduced is expected to be low. Calculations for the range of $\pm 50^\circ\text{C}$ were also completed to assess the reliability of the derived data, these figures emphasise that uncertainties in the temperatures used to calculate fractionations will generally produce small errors in the estimated fluid compositions and could not affect the conclusions in any substantive way.

Table 7-3 Mineral-H₂O fractionation equations for oxygen (Temperature (T) is in Kelvin)

Mineral	Fractionation equation	Reference
Dolomite: CaMg(CO ₃) ₂	$3.06 \times 10^6 / (T)^2 + 10^3 / T - 3.24$	Matthews and Katz (1977)
Diopside: CaMgSi ₂ O ₆	$3.92 \times 10^6 / (T)^2 - 8.43 \times 10^3 / T + 2.4$	Zheng (1993)
Andradite: Ca ₃ Fe ₂ Si ₃ O ₁₂	$3.76 \times 10^6 / (T)^2 - 9.05 \times 10^3 / T + 2.52$	Zheng (1993)
Grossular: Ca ₃ Al ₂ Si ₃ O ₁₂	$3.74 \times 10^6 / (T)^2 - 9.11 \times 10^3 / T + 2.52$	Zheng (1993)
Humite: (Mg,Fe) ₇ (SiO ₄) ₃ (F,OH) ₂	$3.77 \times 10^6 / (T)^2 - 9.01 \times 10^3 / T + 2.51$	Zheng (1993)
Phlogopite: KMg ₃ AlSi ₃ O ₁₀ (OH) ₂	$3.86 \times 10^6 / (T)^2 - 8.68 \times 10^3 / T + 2.45$	Zheng (1993)
K-feldspar: KAlSi ₃ O ₈	$4.32 \times 10^6 / (T)^2 - 6.27 \times 10^3 / T + 2.0$	Zheng (1993)
Quartz: SiO ₂	$4.48 \times 10^6 / (T)^2 - 4.77 \times 10^3 / T + 1.71$	Zheng (1993)
Magnetite: Fe ₃ O ₄	$3.02 \times 10^6 / (T)^2 - 12.0 \times 10^3 / T + 3.31$	Zheng (1993)
Biotite: K(Mg,Fe) ₃ (Si ₃ Al)O ₁₀ (OH,F) ₂	$3.84 \times 10^6 / (T)^2 - 8.76 \times 10^3 / T + 2.46$	Zheng (1993)
Tremolite: Ca ₂ Fe ₅ Si ₈ O ₂₂ (OH) ₂	$3.95 \times 10^6 / (T)^2 - 8.28 \times 10^3 / T + 2.38$	Zheng (1993)
Serpentine: Mg ₃ Si ₂ O ₅ (OH) ₄	$3.99 \times 10^6 / (T)^2 - 8.12 \times 10^3 / T + 2.35$	Zheng (1993)
Anhydrite: CaSO ₄	$3.21 \times 10^6 / (T)^2 + 10^3 / T - 4.72$	Chiba et al. (1981)
Muscovite: KAl ₃ Si ₃ O ₁₀ (OH) ₂	$4.1 \times 10^6 / (T)^2 - 7.61 \times 10^3 / T + 2.25$	Zheng (1993)
Talc: Mg ₃ Si ₄ O ₁₀ (OH) ₂	$4.2 \times 10^6 / (T)^2 - 7.04 \times 10^3 / T + 2.14$	Zheng (1993)
Calcite: CaCO ₃	$4.01 \times 10^6 / (T)^2 - 4.66 \times 10^3 / T - 0.06$	Zheng (1993)


Table 7-4 Mineral-H₂O fractionation equations for hydrogen (Temperature (T) is in Kelvin)

Mineral	Fractionation equation	Reference
Phlogopite: KMg ₃ AlSi ₃ O ₁₀ (OH) ₂	$-22.4 \times 10^6 / (T)^2 + 10^3 / T + 27.1$	Suzuoki and Epstein (1976)
Biotite: K(Mg,Fe) ₃ (Si ₃ Al)O ₁₀ (OH,F) ₂	$-21.3 \times 10^6 / (T)^2 + 10^3 / T - 2.8$	Suzuoki and Epstein (1976)
Tremolite: Ca ₂ Fe ₅ Si ₈ O ₂₂ (OH) ₂	$-31.0 \times 10^6 / (T)^2 + 10^3 / T + 14.9$	Graham et al. (1984)
Serpentine: Mg ₃ Si ₂ O ₅ (OH) ₄	$27.5 \times 10^6 / (T)^2 - 76.9 \times 10^3 / T + 40.8$	Sakai and Tsutsumi (1978)
Muscovite: KAl ₃ Si ₃ O ₁₀ (OH) ₂	$-22.1 \times 10^6 / (T)^2 + 10^3 / T + 19.1$	Suzuoki and Epstein (1976)

Table 7-5 Mineral-SO₄/H₂S fractionation equations for sulphur (Temperature (T) is in Kelvin)


Mineral	Fractionation equation	Reference
Anhydrite: CaSO ₄	$4.26 \times 10^6 / (T)^2 + 10^3 / T + 6.0$	Ohmoto and Rye (1979)
Pyrite: FeS ₂	$0.4 \times 10^6 / (T)^2 + 10^3 / T$	Ohmoto and Rye (1979)
Chalcopyrite: CuFeS ₂	$-0.05 \times 10^6 / (T)^2 + 10^3 / T$	Ohmoto and Rye (1979)
Covellite: CuS	$-0.4 \times 10^6 / (T)^2 + 10^3 / T$	Ohmoto and Rye (1979)
Sphalerite: ZnS	$0.4 \times 10^6 / (T)^2 + 10^3 / T$	Ohmoto and Rye (1979)
Galena: PbS	$-0.63 \times 10^6 / (T)^2 + 10^3 / T$	Ohmoto and Rye (1979)

Figure 7-2 Fractionation curves for oxygen (a-d), hydrogen (e) and sulphur (f)

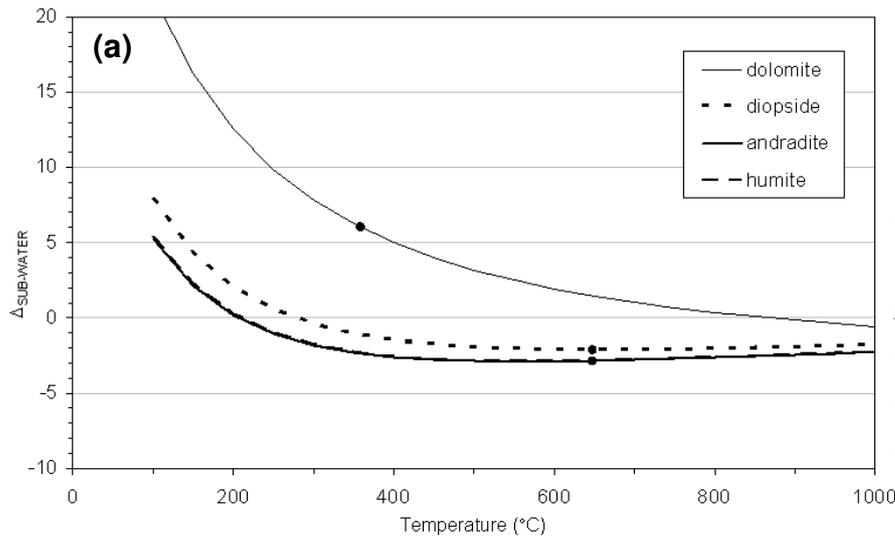

Isotope fractionation curves generated from equations in Table 7-3, Table 7-4 and Table 7-5. (a) (b) (c) (d) oxygen (e) hydrogen (f) sulphur. A dot has been placed on each curve to indicate the temperature that was used to calculate the isotope composition of the fluid for each mineral.

The oxygen fraction curves indicate that lower temperatures than those selected will result in higher fractionation values, except for magnetite, while lower temperatures than those selected will result in comparatively lower fractionation values for hydrogen (except serpentine).

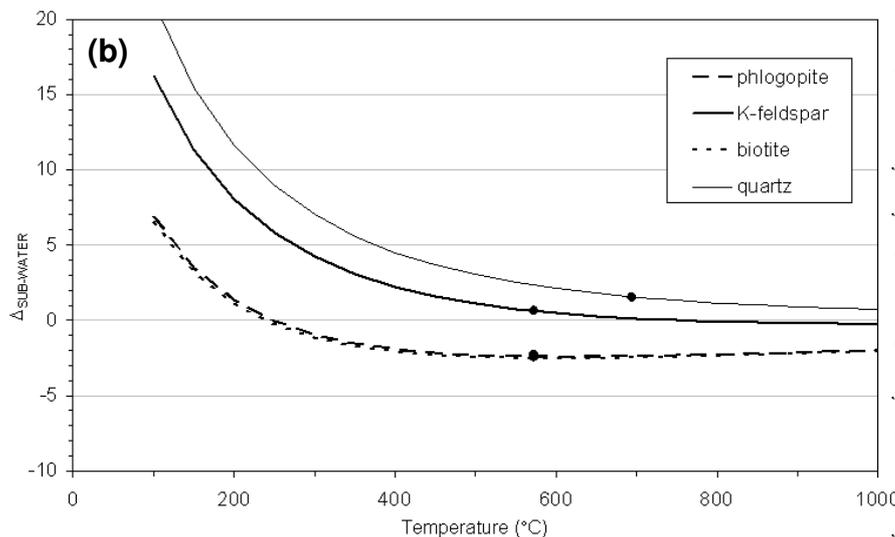

As the fractionation curves for skarn (a) and potassic (b) minerals have gentle slopes near the temperature selected (dots), the assumed temperatures are considered sound. No data exists for estimating temperature of magnetite formation, however, the fractionation curves are very gentle in the vicinity of the temperature chosen.




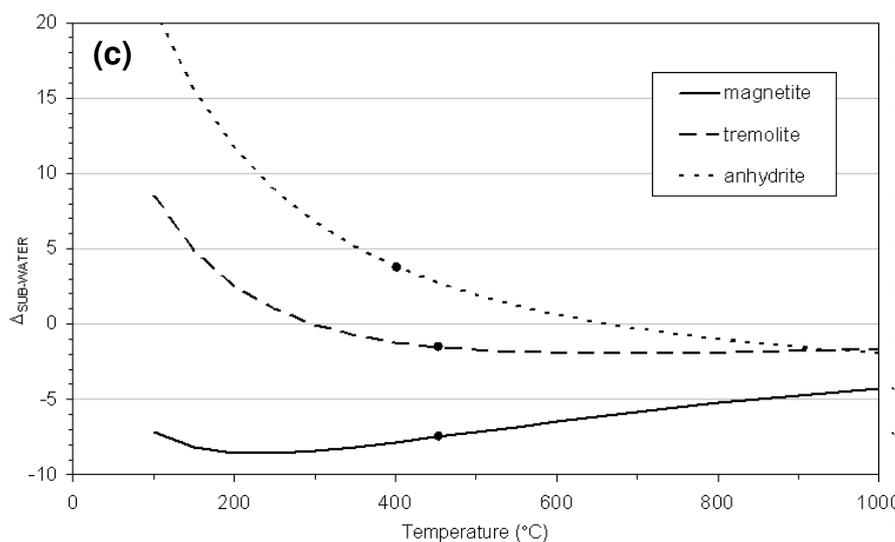


Figure 7-2 Fractionation curves for oxygen (a-d), hydrogen (e) and sulphur (f) (cont)

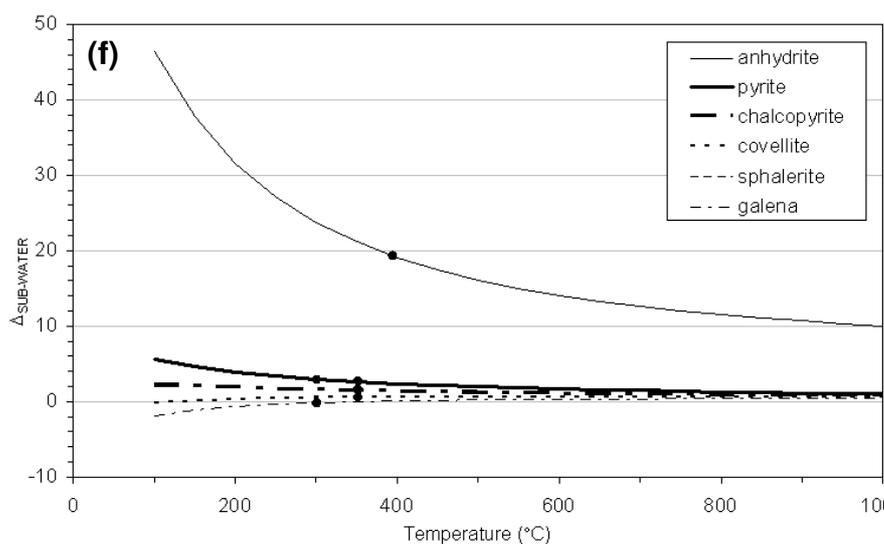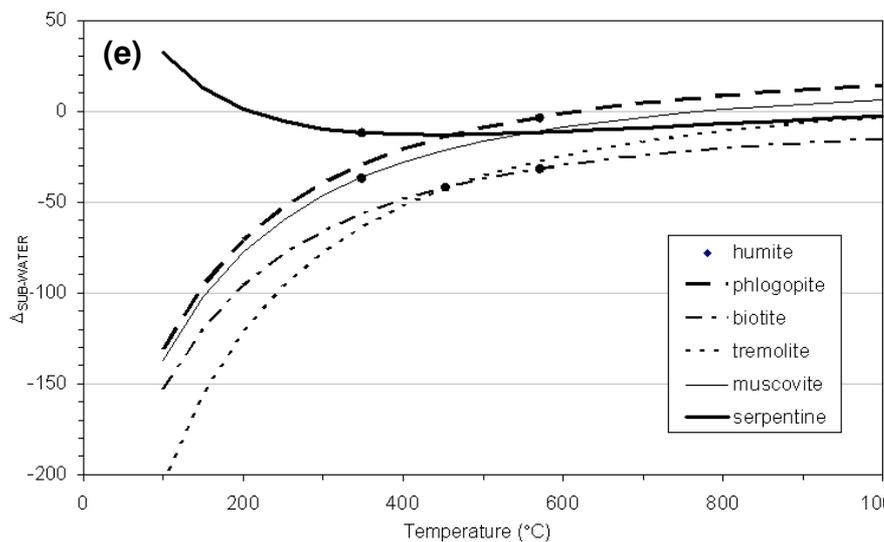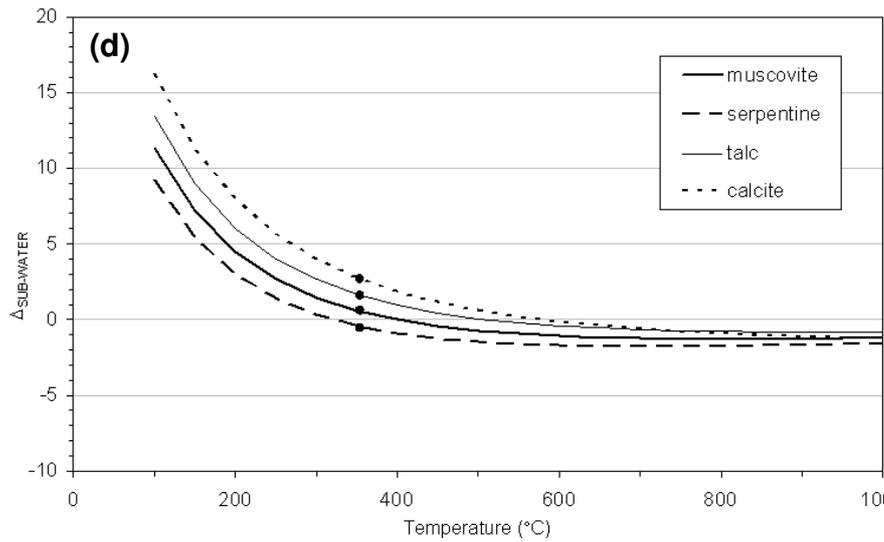

Although tremolite and anhydrite have relatively large slopes the temperatures are thought to be robust (see Discussion) Dolomite and anhydrite may have the greatest temperature uncertainty-related error, as the assumed temperatures used to calculate fluid compositions for these minerals lay along steep sections of their respective fractionation curves. Although the assumed temperatures of minerals in (d) lie on segments of high slope the formation temperatures are constrained by fluid inclusion homogenisation temperatures (Chapter 6) in related quartz alteration. (f) Predicts higher ^{34}S fractionation differences at lower temperatures for anhydrite. As sulphide-fluid fractionations are small the possibility of a large error on calculated fluid composition is also small. Sulphur isotope fractionation is less sensitive to temperature for sulphides than for anhydrite.

Results of fractionation calculations

Estimated $\delta^{18}\text{O}_{\text{FLUID}}$ displays a positively skewed distribution between 0 and 12‰ with the majority of samples between 4 and 10‰ $\delta^{18}\text{O}$ and a maximum at 8-9‰ (Figure 7-3a). Dolomitisation fluids fall outside the main range of fluid compositions, having significantly higher $\delta^{18}\text{O}$ of 16-17‰. Group I diopside, garnet, humite and phlogopite plus Group II quartz veins and magnetite formed from fluids with restricted range of $\delta^{18}\text{O}$ between 4 and 10‰. Individually, each of these minerals imply $\delta^{18}\text{O}_{\text{FLUID}}$ values do not vary by more than 2‰. δD of fluid for Group I minerals are preserved in humite and phlogopite which have a large but evenly spread range of values between -225 and -150‰ (Figure 7-3b). Group III biotite and tremolite-actinolite have distinct fluid compositions. While biotite fluid compositions are a single population restricted between 5 and 7‰ $\delta^{18}\text{O}$ (Figure 7-3a) and -175 to -150‰ δD (Figure 7-3b), tremolite-actinolite fluids are in two groups of 4-5‰ and 8-10‰ $\delta^{18}\text{O}$ (Figure 7-3a). $\delta\text{D}_{\text{FLUID}}$ derived from these two minerals range between -175 to -125‰ and -100 to -75‰ δD (Figure 7-3b). Fluids associated with Group III quartz alteration appear to have had a large and continuous variation in $\delta^{18}\text{O}$ from 6 to 0‰ (Figure 7-3a). Group III anhydrite precipitated from fluids with $\delta^{18}\text{O}$ near 0‰ and $\delta^{34}\text{S}$ from -12 to -8‰. Muscovite fluids had $\delta^{18}\text{O}$ between 5 and 7‰ and the highest δD recorded for all fluids between -75 and -50‰ (Figure 7-3b). Talc fluids have lower $\delta^{18}\text{O}$ between 3 to 4‰ $\delta^{18}\text{O}$ (Figure 7-3a). Calculated $\delta^{34}\text{S}_{\text{FLUID}}$ for pyrite overlaps with those for anhydrite ranging from -10 to -2‰ with a concentration between -8 and -4‰ (Figure 7-3c). $\delta^{34}\text{S}_{\text{FLUID}}$ values for chalcopyrite and covellite are similar, each having some values close to 0‰ as well as a second group of $\delta^{34}\text{S}_{\text{FLUID}}$ similar to values for pyrite fluids between -8 and -4‰ (Figure 7-3c). The single samples of sphalerite and galena give comparable values close to 0‰ similar to chalcopyrite and covellite values. Calcite infill that post-dates pyrite alteration and occurs as fracture infill along with high sulphidation nukundamite mineralisation has a calculated $\delta^{18}\text{O}_{\text{FLUID}}$ between 6 and 7‰ (Figure 7-3a).

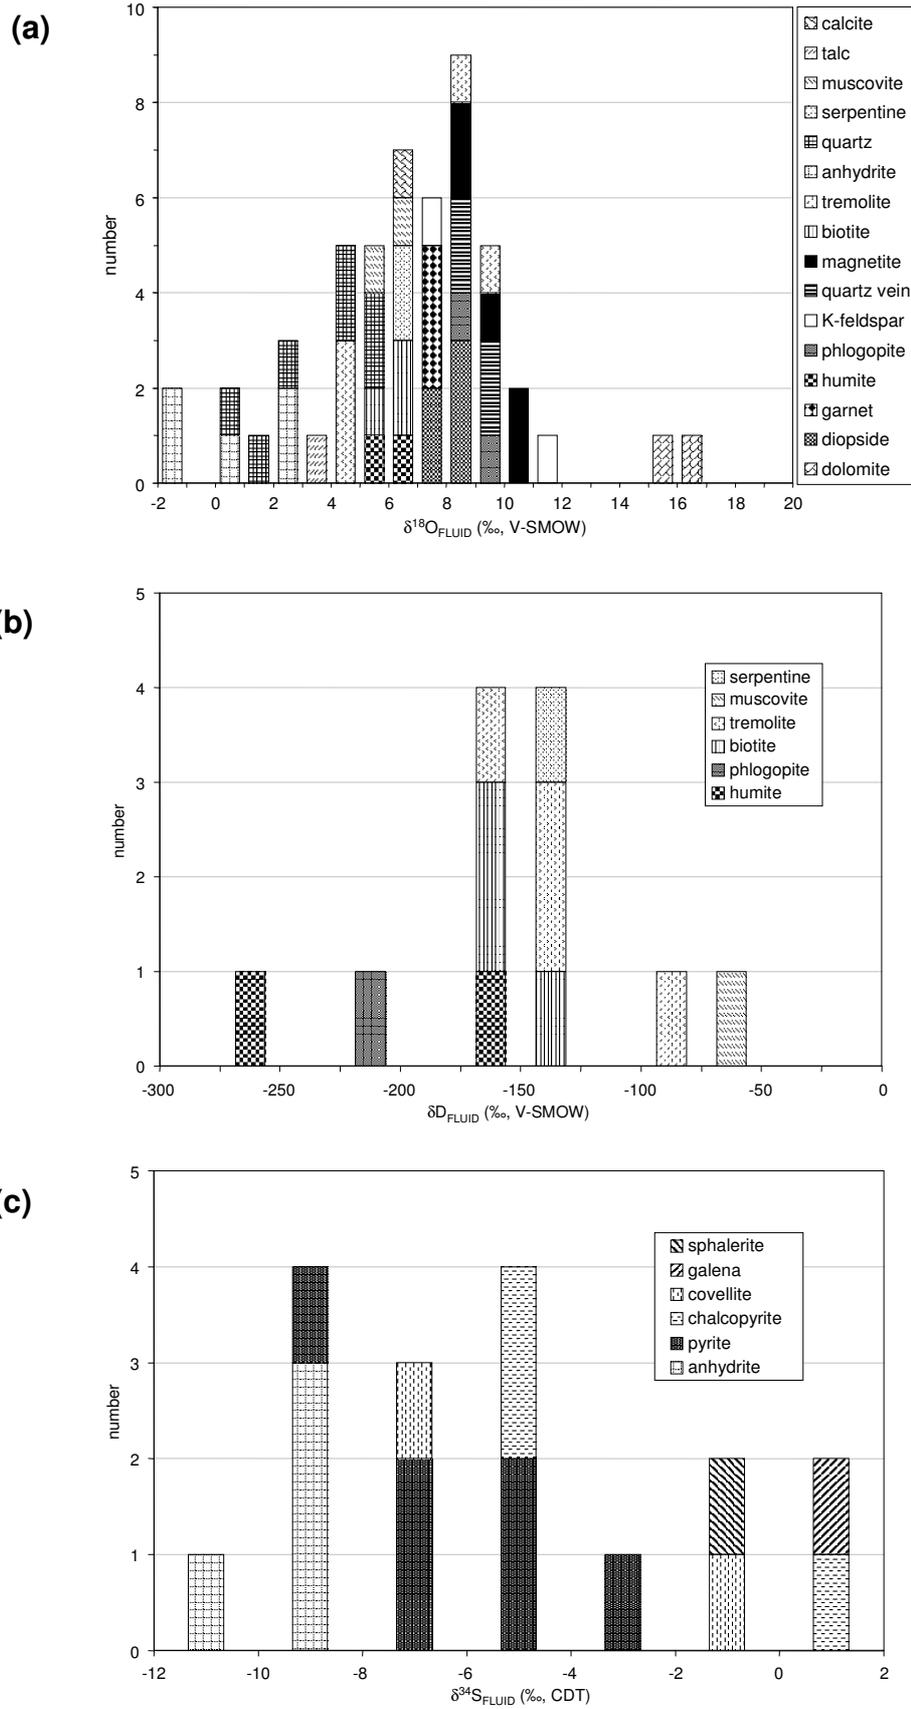


Figure 7-3 Histograms showing calculated oxygen, hydrogen and sulphur isotope ratios

7.2 INTERPRETATION

Stable isotopes, in particular oxygen and hydrogen, have been used to constrain the origin of hydrothermal fluids in Kucing Liar. Oxygen isotope compositions have been used to great effect in understanding the origin of fluids in geological environments. Restricted ranges of oxygen compositions for waters derived from deep-sea sediments, limestone, metamorphism and magmas have been established and are reported as enrichment or depletion in ^{18}O relative to Standard Mean Ocean Water (SMOW) measured at the equator. However, studies in the North American continent reveal that isotope fractionation is affected by elevation as well as latitude (Taylor, 1979). As elevation increases, both $\delta^{18}\text{O}$ and δD become progressively lower due to fractionation of oxygen and hydrogen during evaporation and precipitation. As such, data from local snow, glacial ice and mine water, which indicate values of -125‰ δD and -15‰ $\delta^{18}\text{O}$ (Harrison, 2000) may not be valid for comparison against fossilised hydrothermal systems due to the potentially dramatic changes in elevation in such an active environment and the potentially large amount of uplift that has occurred since hydrothermal activity. Local studies at Big Gossan (Meinert *et al.*, 1998) and regional studies of the Southern Ranges (Weiland and Cloos, 1996) have arrived at comparable figures of 2km for erosion and uplift within the district. The current uplift of 1mm/y for New Guinea could have produced 3km of uplift in the 3Ma since mineralisation occurred. This relatively dramatic change in elevation for the Ertsberg Mining District will cause the $\delta^{18}\text{O}$ and δD of local meteoric waters at the time of mineralisation to be different from those of contemporary waters. As such, the local meteoric water compositions at the time of hydrothermal activity may have been similar to SMOW, and for simplicity in discussion, are treated as such.

Fluid reservoirs and isotopic compositions

The distinct isotopic signature of dolomitisation in Kucing Liar samples matches that of basin waters, which are expelled from the sediments during orogenesis (*cf.* Hitzman *et al.*, 1997). By contrast, Group I skarn and Group II potassic fluids all fall within the range of magmatic water. Quartz and anhydrite from Group III have $\delta^{18}\text{O}_{\text{FLUID}}$ in part similar to SMOW, ranging up to

compositions of magmatic waters. The systematic variation of isotopic compositions can arise from the gradual mixing of magmatic and local waters (Campbell and Larson, 1998). The progressive shift toward lower values observed in Groups I & II may be the result of minor interaction with meteoric waters, while the oxygen isotope composition of quartz indicates total interaction with a fluid of meteoric water composition. $\delta^{18}\text{O}$ values of anhydrite from Group III also indicate derivation of oxygen from fluids with compositions similar to those of standard mean ocean waters (SMOW).

Estimated fluid compositions during the earliest stages of alteration display relatively homogeneous $\delta^{18}\text{O}$, and these compositions are shifted significantly from values of $\delta^{18}\text{O}$ collected from two samples of dolomitic wall rocks. This would suggest that composition of the wall rocks have no influence of hydrothermal alteration, indicating that the oxygen component of the original carbonate rocks has been completely replaced by the introduced fluid. This is most likely due to high fluid-rock ratios, or in other words that the Kucing Liar is fluid-buffered. Skarn vein material is shifted significantly from that of the sampled dolomite. Three minerals analysed from the skarn group display a progressive decrease with paragenetic time (Figure 7-4). This may indicate some large-scale effect on the fluids by local conditions while the gradual progression in ^{18}O compositions indicates evolution of a common fluid source or mixing with local isotope sources. There is a major change in composition between the composition of calc-magnesian silicate minerals and that of phlogopite alteration, which was assigned to Group I skarn in Chapter 2. The large compositional change is thought to indicate a different fluid source for phlogopite from calc-magnesian skarn. The hydrogen isotope analyses are less exhaustive but display a different relationship in skarn minerals. Two humite samples have very different δD , while a single phlogopite analysis reports a δD value between the two samples of humite.

Sulphur isotopes have also been analysed for anhydrite as well as the primary sulphides and indicate a range from a source depleted in ^{34}S for anhydrite, a source equivalent to primary magmatic sulphur for some of the copper mineralisation, and a source for sulphur that is mixed

between these two end-members. Sulphur isotope data from Kucing Liar are difficult to interpret due to a lack of knowledge concerning details of the fractionation of ^{34}S during fluid evolution and in fluid-rock reactions (*cf.* Ohmoto and Rye, 1979). While the origin of sulphur is elusive, some appreciation can be gained from comparison of data from different minerals. The sulphur in anhydrite is depleted in ^{34}S compared to pyrite, which exhibits a range in compositions, and base metal sulphides have compositions similar to primary magmatic sulphur. As anhydrite is likely to be derived from strongly mixed magmatic-meteoric waters (see above) it is assumed that the depleted ^{34}S values of anhydrite indicate meteoric mixing, leading to an interpretation where the range of pyrite values represents variable mixing between the primary magmatic and non-magmatic sulphur anhydrite.

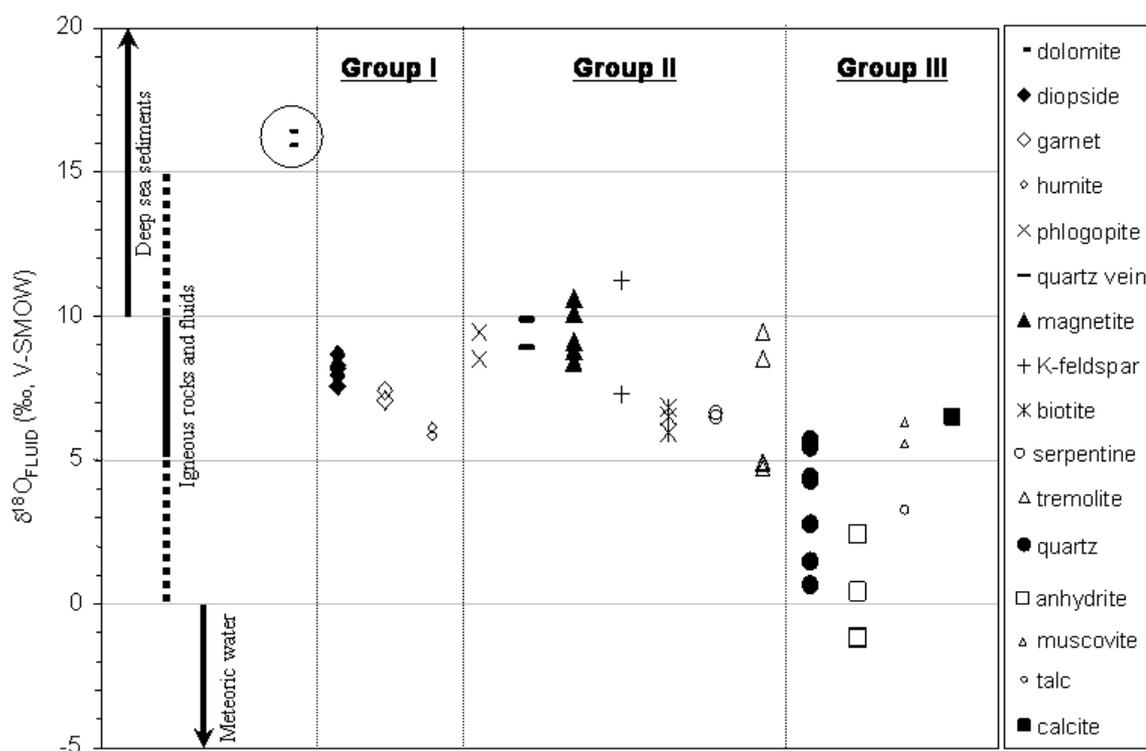


Figure 7-4 Calculated $\delta^{18}\text{O}_{\text{FLUID}}$ for the Kucing Liar paragenesis

Calculated $\delta^{18}\text{O}_{\text{FLUID}}$ arranged in paragenetic sequence illustrate the magmatic affinity of Group I-III as well as their systematic variation. Ranges for fluid reservoirs are from Campbell and Larson (1998).

Magmatic exsolution processes

While oxygen compositions distinguish between ultimate fluid sources, hydrogen isotope compositions can also identify melt-fluid-vapour interactions within the parent magma. As the mass difference between hydrogen and deuterium is 100%, it is the most sensitive to fractionation processes (e.g. Campbell and Larson, 1998) and thus may indicate subtle influence more readily than oxygen isotopes. As deuterium is preferentially fractionated into vapour at high temperatures, a partially degassed magma will be left isotopically lighter in terms of hydrogen (Taylor, 1988). Fluids are either passively exsolved from their magmatic source or are ponded at the upper carapace (Burnham, 1979). Gradual removal of a deuterium-enriched vapour will cause the residual magma and any subsequently derived fluids to have progressively lower δD . However, vapour ponding and catastrophic release will cause the release of fluids with homogenous δD (Taylor, 1988; Taylor, 1997). In this way, magma degassing can account for both clustering (closed system) and large variations (open system) of deuterium compositions due to the preferential fractionation of deuterium into an escaping gas phase (Taylor, 1988; Hedenquist and Richards, 1998). Open system degassing can produce deuterium depletions down to -140% for small water fractions, which has been corroborated by observations of natural systems where there is direct correlation between low δD and low remaining fractions of wt% H_2O as determined from gas trapped in lava (Taylor, 1988).

Hydrogen isotope analyses conducted on a small group of samples indicates that magnesian skarn, represented by humite and green phlogopite, formed from fluids with variable but consistently very low δD values. By contrast, Group II biotite fluids, although still much lower than primary magmatic waters are tightly clustered about -150% . Tremolite-actinolite fluids also have a large range in δD values that are lower than primary magmatic waters, whereas these minerals suggest little variation in $\delta^{18}O_{FLUID}$. The development of very low δD values in hydrothermal minerals may result from degassing of magma prior to fluid exsolution. The trend of increasing δD with time for Kucing Liar fluids is opposite to what is expected to result from continued exsolution of

a finite water source from magma chamber. This could indicate mixing with isotopically “heavier” local meteoric waters, or replenishment of the source area with new magma influxes, which would “reset” the δD values for new fluid fractions. If this were the case, replenishment would have had to have occurred prior to potassic alteration and again prior to phyllic alteration.

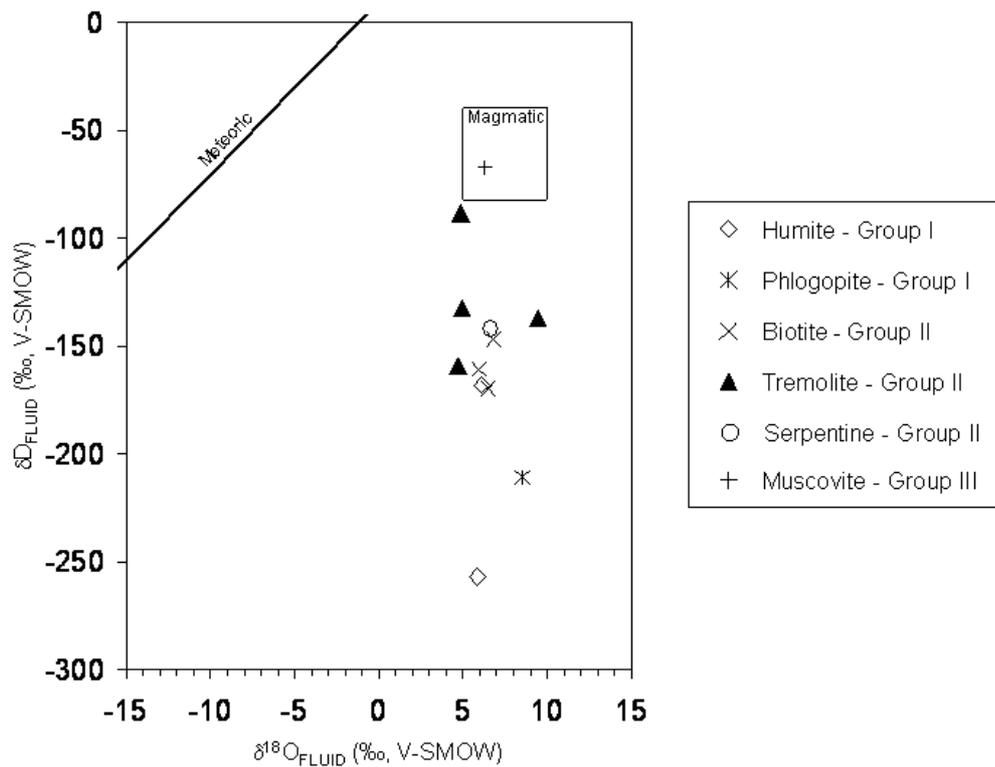


Figure 7-5 Calculated Hydrogen and oxygen isotope compositions of Kucing Liar fluids
Magmatic box based on Campbell and Larson (1998) and meteoric water line from Craig (1961).

8 $^{40}\text{Ar}/^{39}\text{Ar}$ geochronology

The primary geochronological tool used was ^{40}Ar - ^{39}Ar dating, providing a much higher degree of precision than K-Ar published dates in the Ertsberg Mining District. Re-Os dates of molybdenite are also presented. These methods are reported to be comparable in terms of accuracy and high precision (Richards and Noble, 1998). It has been suggested that Re-Os dating techniques are more reliable than other dating techniques as it is not susceptible to resetting due to thermal disturbances post-formation, and that, together with ^{40}Ar - ^{39}Ar , provides the most accurate ages for mineralisation (Stein *et al.*, 1997). The use of Re-Os has been found to be reproducible and able to give an age for mineralisation even in disturbed terranes (Watanabe and Stein, 2000). Two green phlogopite samples, three biotite samples and two muscovite samples of pure mineral material were despatched to Lisa Peters at the New Mexico Geochronology Research Laboratory (NMGRL) and a single sample containing molybdenite was delivered to Ryan Mathur at the University of Arizona for Re-Os analyses. Details of the analytical procedures followed by each laboratory are included in Appendix VIII. Minerals suitable for $^{40}\text{Ar}/^{39}\text{Ar}$ geochronometry are restricted to phases containing >0.3wt% K_2O content and were chosen to represent two separate groups of paragenetic assemblages; green phlogopite and biotite represent latest skarn and potassic alteration while muscovite represents the Group III assemblage. Samples of pure mineral were generated by hand picking grains and clusters of grains from pulverised rock sample after splitting to 250 μm size fractions. Green phlogopite places a maximum age constraint for potassic alteration and a minimum age for skarn development, while biotite is considered to place minimum age constraints on potassic alteration. Together, these two micas should reveal the time-scale for potassic alteration. Muscovite provides a minimum age of quartz alteration and a maximum age for covellite-bearing mineralization. Molybdenite is expected to place a minimum age on covellite-bearing high sulphidation mineralization as it overprinted covellite (Chapter 3).

8.1 SAMPLE COLLECTION

Mineralogical and textural/relative timing descriptions plus a photograph (Figure 8-1 & Figure 8-2) is provided for each sample from which pure mineral separates were collected. The samples in paragenetic order are:

- KL28-1 360.3m, composed of very coarse-grained green phlogopite, vein K-feldspar, magnetite fracture infill and chalcopyrite alteration/infill spots (Figure 8-2a). The phlogopite that was extracted is penetrative alteration of an unknown precursor and is restricted to a 5m drill intersection that marks a spatial transition from a K-feldspar-quartz-muscovite-pyrite-covellite-native sulphur assemblage to intense magnetite-pyrite-chalcopyrite replacement of unknown lithology and is interpreted to be within a fault zone (see Chapter 3). Petrographically this phlogopite has pale green pleochroism.
- KL32-8 331.0m, composed of strongly fragmented humite-phlogopite-chrysotile-anhydrite-gypsum-serpentine rock (Figure 8-2b). The phlogopite separated consisted of coarse, very pale green to almost colourless idiomorphic grains associated with the fragment of humite-altered rock. Pyrite-chalcopyrite mineralisation is associated with a band of anhydrite-gypsum and is crosscut by serpentine. Petrographically the phlogopite has pale green pleochroism.
- KL32-5 539.6m, composed of coarse-grained red-brown biotite-tremolite-talc-pyrite-chalcopyrite in which the biotite has cross-cut tremolite as centimetre scale selvage alteration (Figure 8-2e). Petrographically the biotite has very pale brown pleochroism and similar transparency to the green phlogopite samples collected from KL28-1 360.3m and KL32-8 331.0m. The sample is from a discrete 5m-scale zone of coarse-grained biotite-tremolite-anhydrite within a 10m-scale zone of magnetite-pyrite-chalcopyrite alteration. Together these are interpreted to represent a fault zone which separates fine-grained K-feldspar-muscovite-pyrite-covellite altered sandstone from clinopyroxene-humite-tremolite-anhydrite altered limestone (see Chapter 3).

-
- KL32-5 652.4m, composed of penetrative K-feldspar and fine and coarse-grained biotite alteration and fracture infill and quartz infill (Figure 8-2c). Petrographically the biotite has dark orange pleochroism. Pure biotite was collected from infill that lines a fracture later infilled with quartz and from intense alteration directly adjacent to the fracture. The sample originates from displaced sections of the upper Waripi shale marker (see Chapter 3) in the footwall of the Idenberg fault zone.
 - KL20-9 465.3m, composed of clinopyroxene-feldspar alteration overprinted successively by quartz veins, magnetite fracture infill and anhydrite alteration. Coarse-grained biotite is associated with the quartz veins (Figure 8-2d). Petrographically the biotite has dark orange pleochroism. It is unclear if the biotite in this sample has overprinted the quartz vein in a crosscutting fracture or if it is wall rock included at the margin of the vein. In the former case it would represent the only identified example of biotite infill in a quartz vein, though there are few examples of definitive relationships between quartz and biotite (see Figure 8-2c). The sample is derived from the lower Ekmai limestone (see Chapter 3).
 - Sample KL32-8 455.9m, a rock affected by semi-penetrative fine to medium-grained muscovite alteration (plus vugh infill) of penetrative K-feldspar alteration (Figure 8-2f). Petrographically the muscovite forms clusters of coarse-grains in vughs and fine-grained accumulations in zones where the underlying K-feldspar can still be identified. The sample also contains vein and fracture selvage alteration comprising anhydrite-pyrite-nukundamite-chalcocite (Figure 8-2f). The sample is collected from the centre of a quartz-muscovite-pyrite alteration zone localised about the Waripi limestone-Ekmai limestone contact (see Chapter 3).
 - Sample KL32-1 255.7m is fine-grained muscovite infill that has grown in millimetre-scale cavities in quartz-altered rock (Figure 8-2g). The muscovite is very fine-grained and the cavities are lined with quartz crystals that protrude inwards (Figure 8-1). Elsewhere, similar vughs are infilled with fluorite-pyrite-covellite. The sample is from a thick section of quartz-

pyrite-muscovite altered drill core at the very top of the mineralised zone that is interpreted to be in the centre of the Idenberg fault zone (see Chapter 3).

- Sample KL42-2 440.5m contains intensely coarse-grained molybdenite mineralisation in K-feldspar-quartz-pyrite alteration (Figure 8-2h). Covellite occurs in the molybdenite clumps and is interpreted to predate the molybdenite. The sample was collected from a K-feldspar-quartz alteration sandwiched between zones of 10m-scale penetrative pyrite alteration that overprinted locally intense magnetite. Although petrological examination was indeterminate concerning the relative timing of covellite and molybdenite, petrographic textures illustrated in Chapter 3 suggest that some molybdenite formed after covellite.

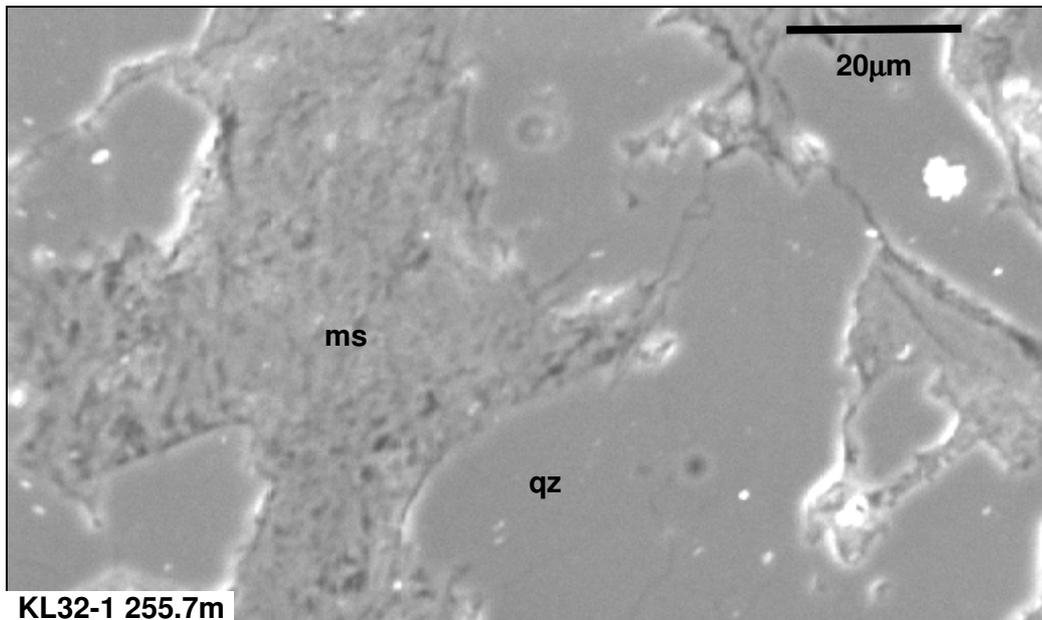


Figure 8-1 Grainsize of muscovite crystals

An SEM image illustrating a cavity surrounded by Group IV quartz alteration infilled with very fine-grained muscovite. The grains of muscovite are only 5-10 μ m in length, which is at the borderline of acceptable grainsize for the $^{40}\text{Ar}/^{39}\text{Ar}$ method.

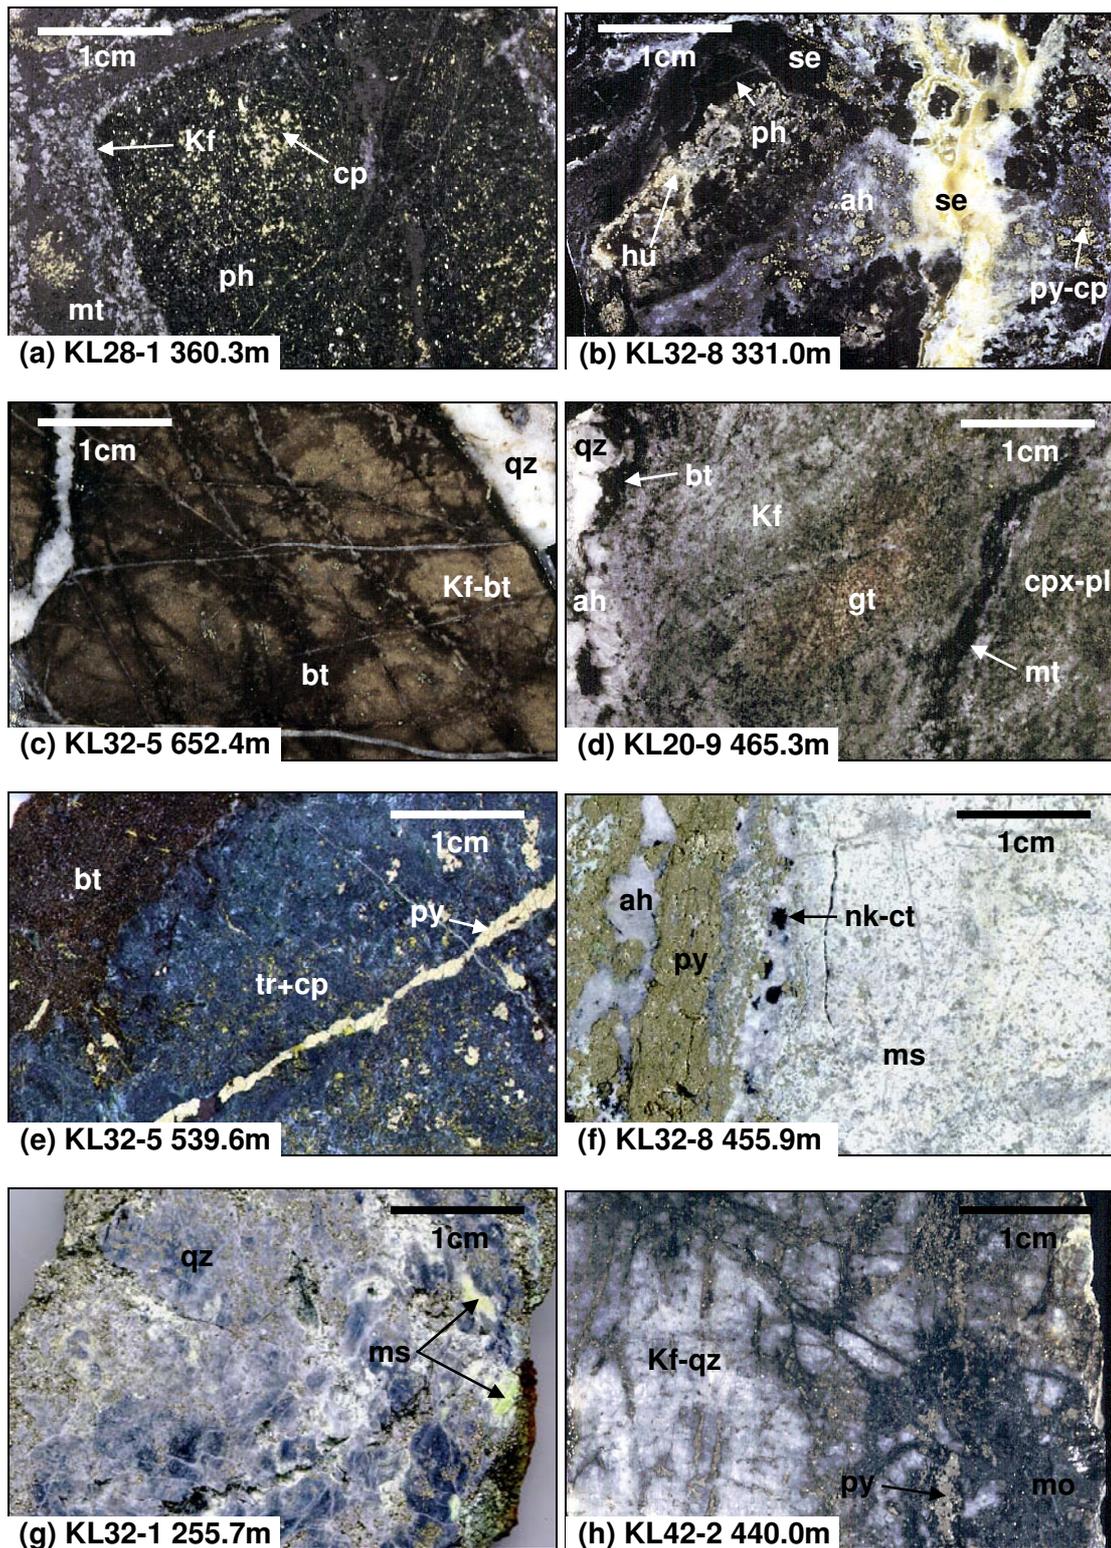


Figure 8-2 Photographs of geochronology samples

(a) & (b) Samples from which pure green phlogopite was extracted for Group I age. (c) (d) & (e) Samples from which pure biotite was extracted for Group II age. (f) & (g) Samples from which pure muscovite was extracted for Group II age (h) Sample from which pure molybdenite was extracted for Re-Os analysis to determine youngest possible age for hydrothermal activity.

8.2 AGE SPECTRA AND RESULTS FROM ANALYSES

The ages established from the results of high precision $^{40}\text{Ar}/^{39}\text{Ar}$ and Re-Os geochronology conducted on alteration minerals are recorded in Table 8-1 and Figure 8-10. All samples except KL28-1 360.3m (green phlogopite) were analysed in the same sample run. $^{40}\text{Ar}/^{39}\text{Ar}$ ages are determined from a plateau or an isochron. A plateau age is defined as the age of contiguous temperature steps whose individual ages overlap within experimental error and whose cumulative $^{39}\text{Ar}_K$ comprises greater than 50% of the total $^{39}\text{Ar}_K$ released from the sample (Snee et al., 1988). The results of step heating are presented as age spectra and isochrons in Figure 8-3 to Figure 8-9 and detailed analyses of the results as reported by the laboratory are included in Appendix VIII.

The ages of green phlogopite samples overlap with one biotite sample. Green phlogopite samples have similar ages with broadly overlapping uncertainties that define a large time period totalling 180ka between $3.42 \pm 0.04\text{Ma}$ and $3.34 \pm 0.07\text{Ma}$ (Table 8-1, Figure 8-10). By contrast, two samples of biotite collected from infill, KL32-5 652.4m and KL20-9 465.3m, have nearly identical ages and age uncertainties recording a total age range for their formation of only 80ka between $3.2 \pm 0.04\text{Ma}$ and $3.18 \pm 0.02\text{Ma}$ (Table 8-1). Biotite collected from selvedge alteration in sample KL32-5 539.6m has an age of $3.28 \pm 0.04\text{Ma}$ which overlaps with both the older green phlogopite and the younger biotite infill. While the mica crystals in this sample are brown-coloured, they are more similar petrographically to the green phlogopite than the biotite infill samples. The two samples of muscovite returned very different ages. Sample KL32-8 455.9m records an age of 3.18 ± 0.02 contemporaneous with biotite infill, while sample KL32-1 255.7m from the uppermost section of the Idenberg fault zone records an age of 3.45 ± 0.06 , which is contemporaneous with green phlogopite (Table 8-1). This age is problematical as textural evidence indicates significant episodes of mineral development occurred between green phlogopite and muscovite.

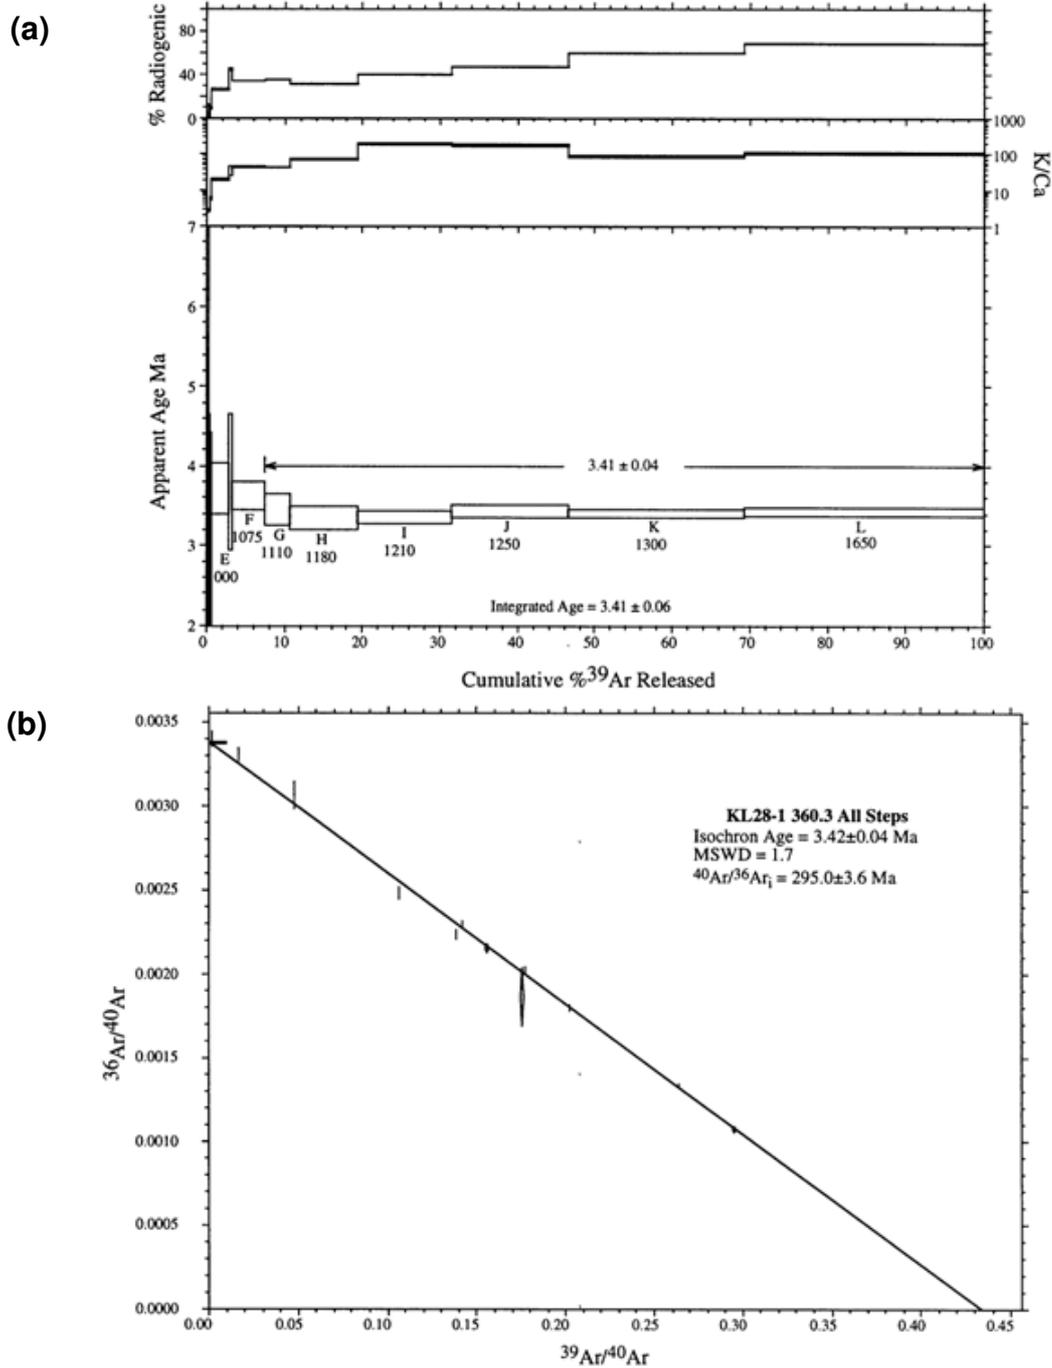


Figure 8-3 Age spectra and isochron plots of sample KL28-1 360.3m (green phlogopite)

The slight downward curve of steps E-H is suggestive of excess ^{40}Ar . This sample was part of a different study and this plot was provided by Pollard (pers comm.) after material initially supplied by Peters (pers comm.).

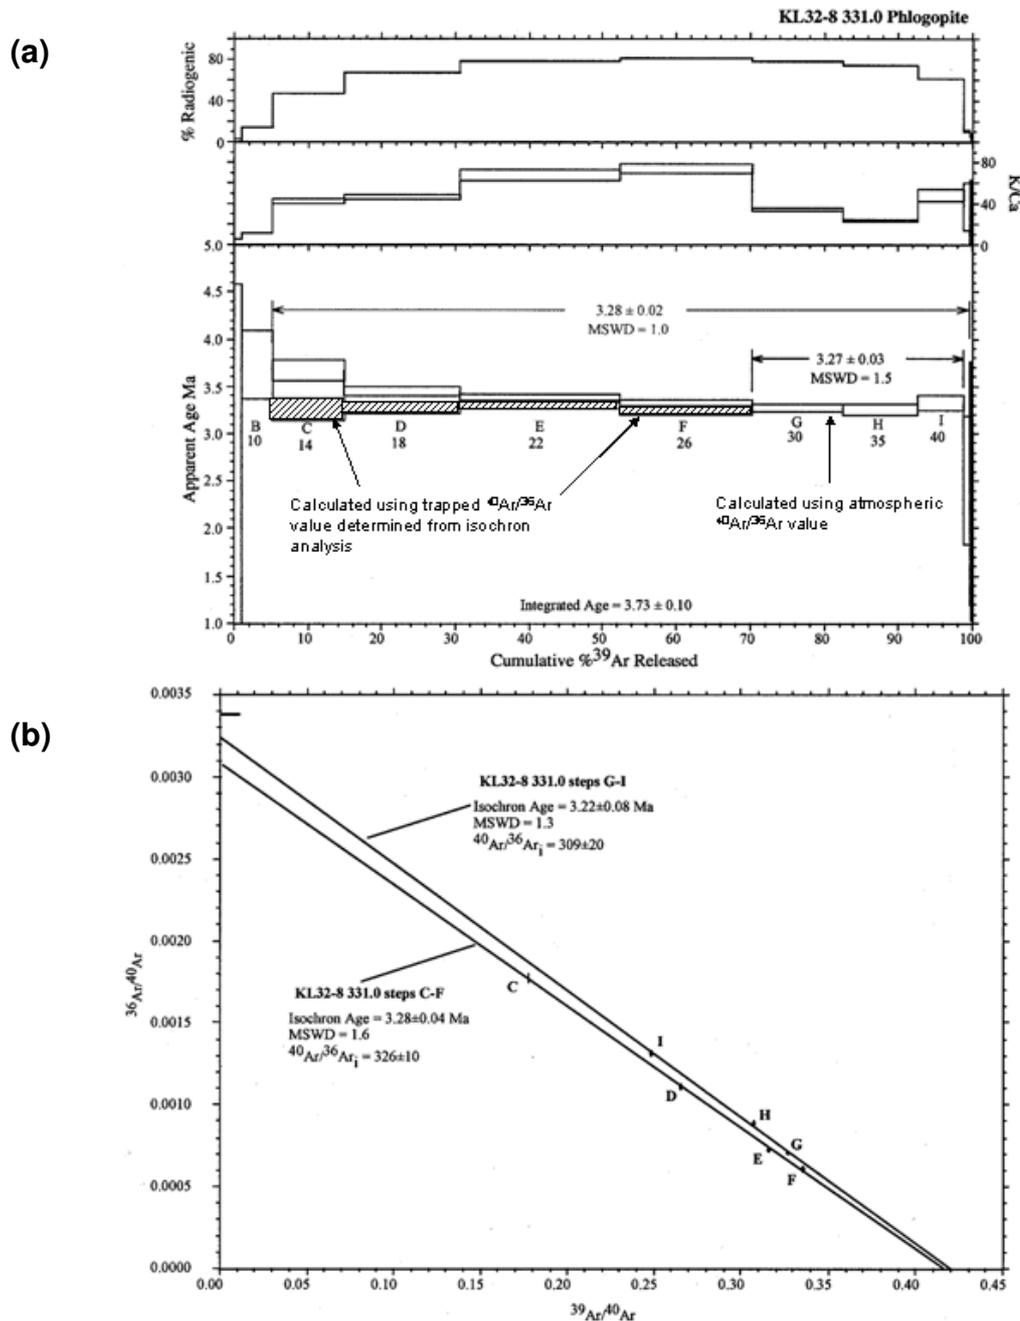


Figure 8-4 Age spectra and isochron plots of sample KL32-8 331.0m (green phlogopite)

The first ~70% of the age spectrum (a) from sample KL32-8 331.0m phlogopite displays decreasing apparent ages correlated with increasing radiogenic yields. A weighted mean age of $3.27 \pm 0.03\text{Ma}$ with an acceptable MSWD is calculated from the remaining portion of the age spectrum. Inverse isochron analysis (b) of this sample reveals two trapped components (Heizler and Harrison, 1988). Steps C-F reveal an age of $3.28 \pm 0.04\text{Ma}$ with a $^{40}\text{Ar}/^{36}\text{Ar}$ intercept of 326 ± 10 and an acceptable MSWD of 1.3. Steps C-F, calculated using the $^{40}\text{Ar}/^{36}\text{Ar}$ ratio indicated by the inverse isochron analysis rather than the atmospheric value that is normally used for age spectrum analysis, are shown plotted with cross hatching on the spectrum diagram. A weighted mean age of $3.28 \pm 0.02\text{Ma}$ is calculated from steps C-F of the isochron analysis and steps G-I of the age spectrum analysis. Figure and discussion reproduced from Peters (pers comm.) (see Appendix VIII).

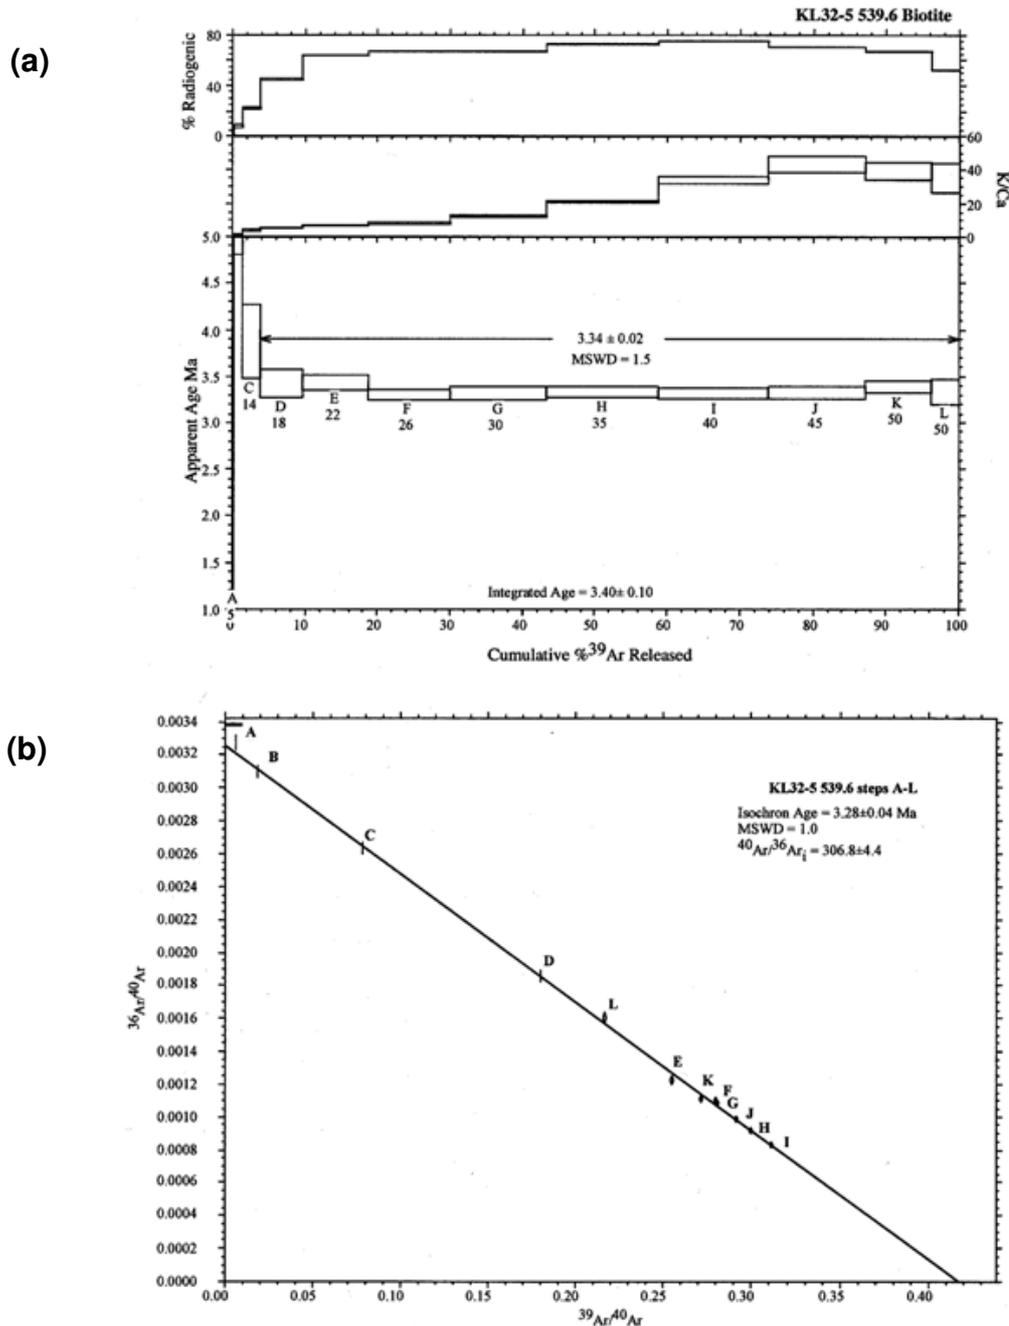


Figure 8-5 Age spectra and isochron plots of sample KL32-5 539.6m (brown biotite)

The slight downward curve of steps C-E (a) is suggestive of excess ^{40}Ar . After the first ~4% of the ^{39}Ar released, the age spectrum from phlogopite sample KL32-5 539.6m is concordant and yields a weighted mean age of $3.34 \pm 0.02\text{Ma}$ with an acceptable MSWD of 1.5 (cf. Mahon, 1996). Inverse isochron analysis (b) of this sample reveals a $^{40}\text{Ar}/^{36}\text{Ar}$ intercept (306.8 ± 4.4) above the atmospheric intercept of 295.5. The isochron age of $3.28 \pm 0.04\text{Ma}$ also has an acceptable MSWD of 1.0. The old apparent ages in the first 10% of the ^{36}Ar released correlates with an increase in radiogenic yield, a pattern often seen in samples that contain excess argon (trapped component greater than atmospheric $^{40}\text{Ar}/^{36}\text{Ar}$ ratio of 295.5). Figure and discussion reproduced from Peters (pers comm.) (see Appendix VIII).

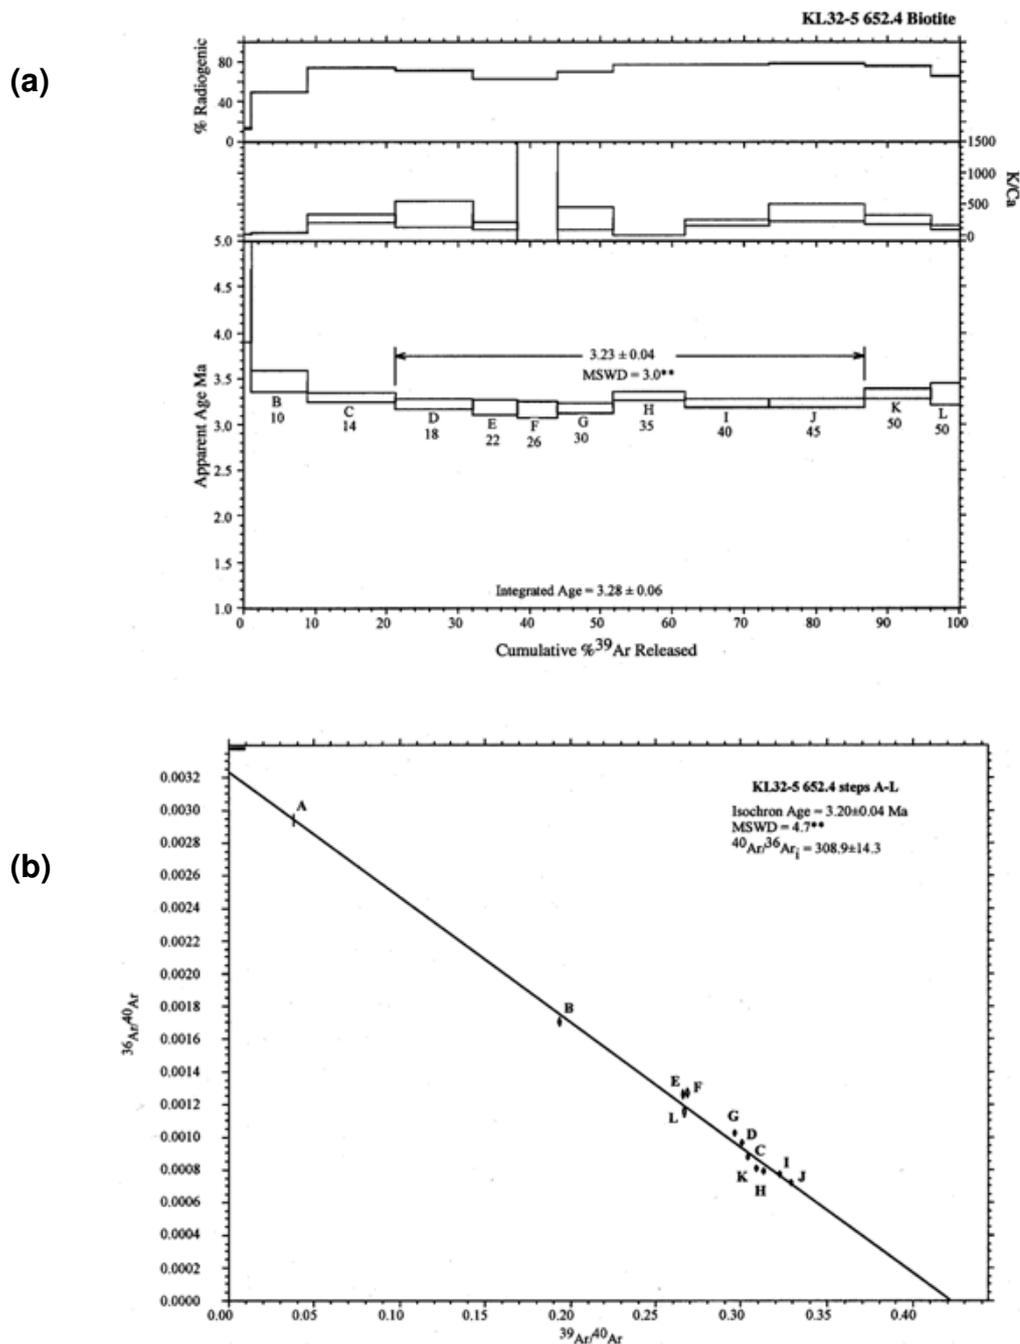


Figure 8-6 Age spectra and isochron plots of sample KL32-5 652.4m (brown biotite)

The first 10-20% of the ^{39}Ar released from phlogopite sample KL32-5 652.4m yields old apparent ages and the remainder of the age spectrum is relatively flat (a). A weighted mean age calculated from steps D-J ($3.23 \pm 0.04\text{Ma}$) has an MSWD value of 3.0, slightly above the acceptable value. When plotted on an inverse isochron (b), an age of $3.20 \pm 0.04\text{Ma}$ is revealed with a $^{40}\text{Ar}/^{36}\text{Ar}$ intercept of 308.9 ± 14.3 . Figure and discussion reproduced from Peters (pers comm.) (see Appendix VIII).

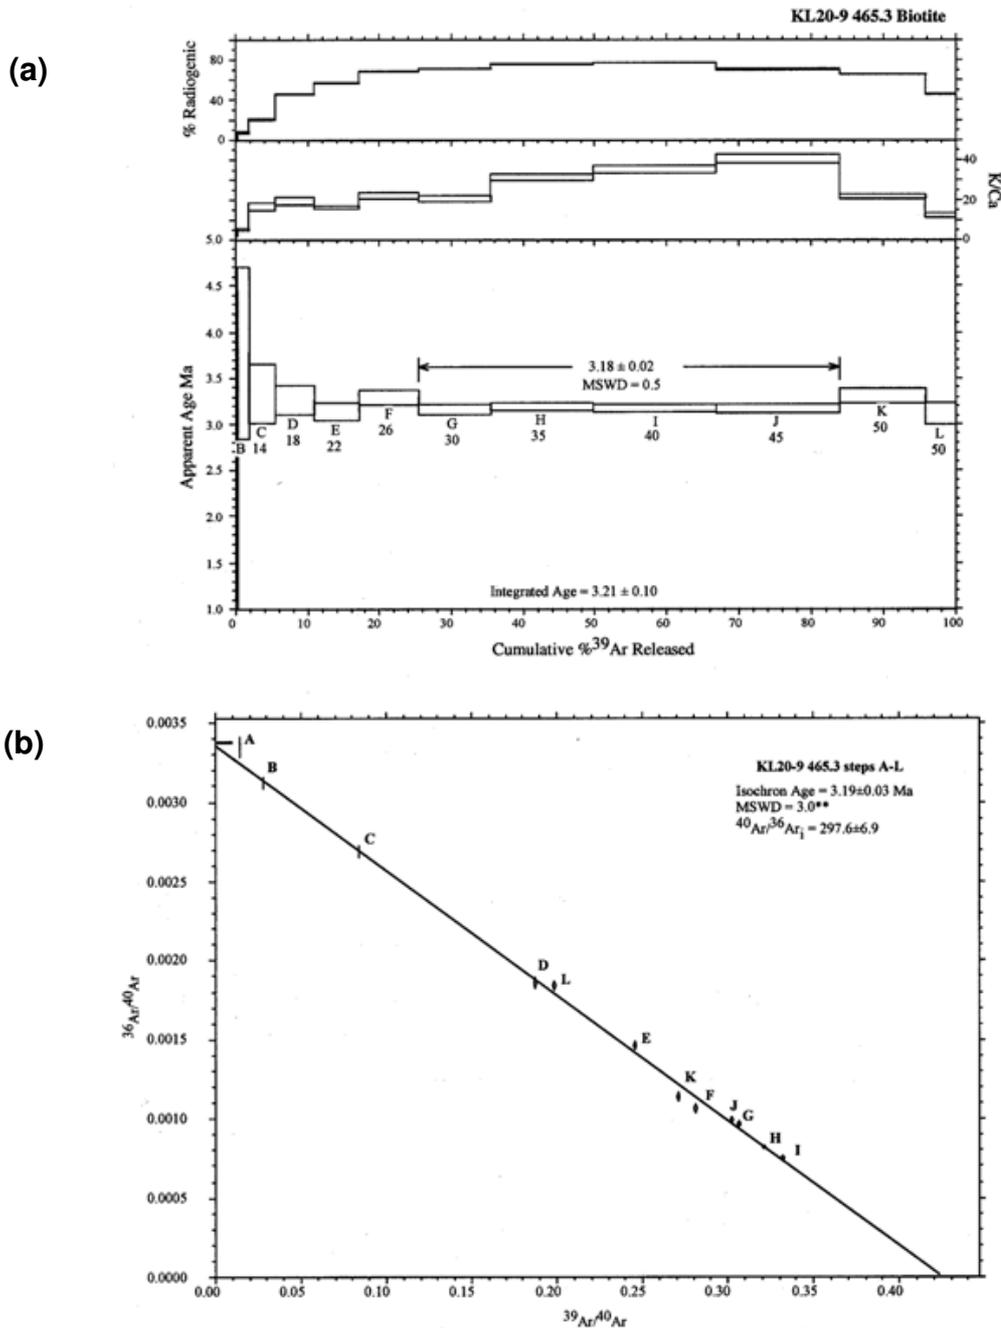


Figure 8-7 Age spectra and isochron plots of sample KL32-5 465.3m (brown biotite)

Phlogopite from sample KL20-9 465.3m yields a nearly concordant age spectrum (a). A weighted mean age of 3.18 ± 0.02 Ma with an acceptable MSWD is calculated for steps G-J. Inverse isochron analysis (b) of steps A-L yields an isochron age of 3.19 ± 0.03 Ma with a $^{40}\text{Ar}/^{36}\text{Ar}$ intercept (297.6 ± 6.9) that agrees within error to the atmospheric ratio. Figure and discussion reproduced from Peters (pers comm.) (see Appendix VIII).

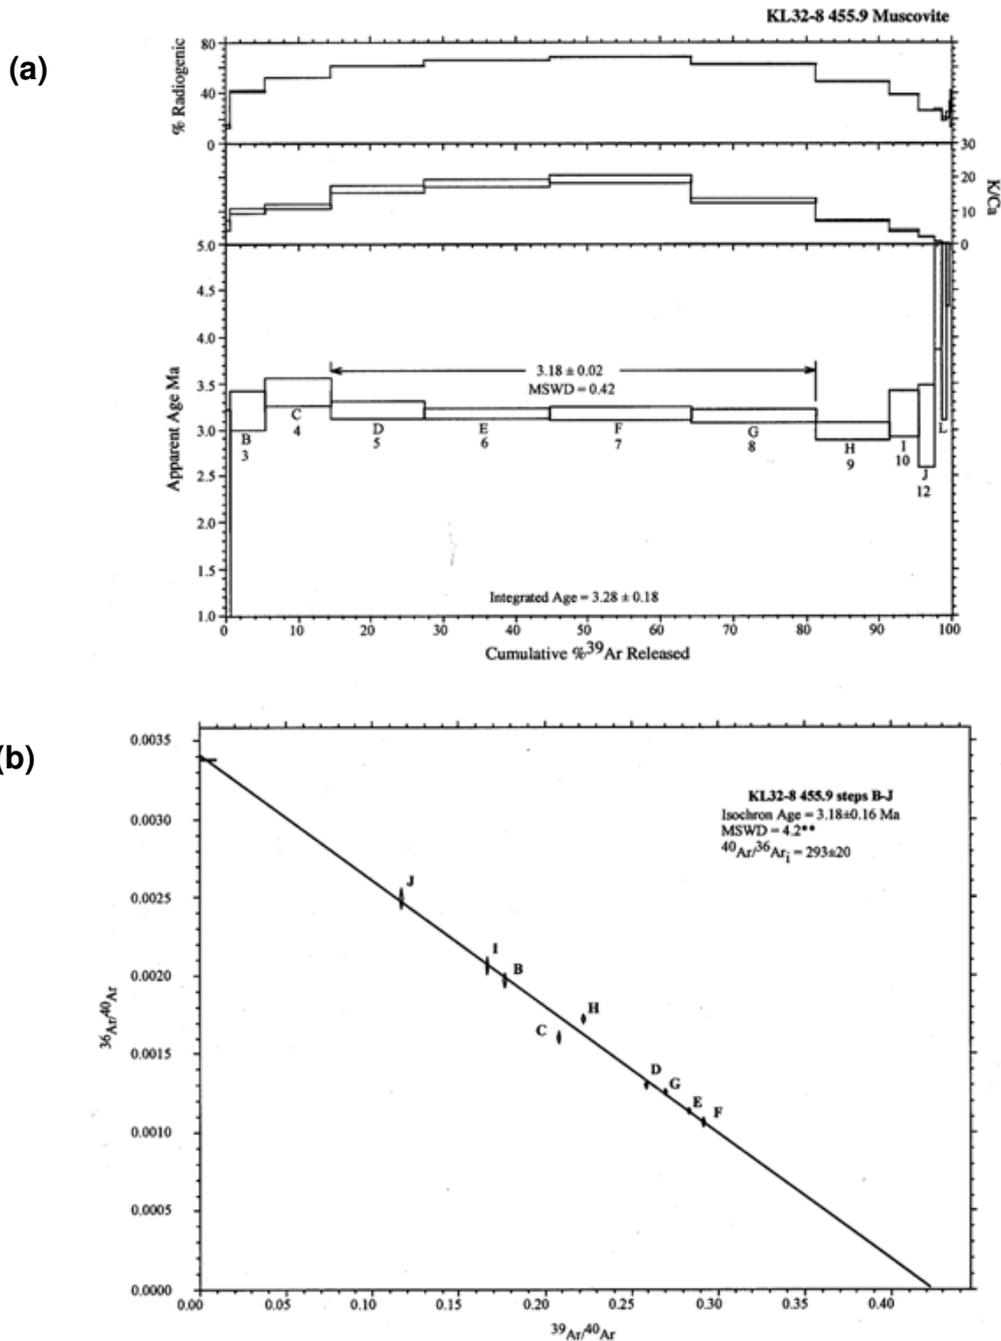


Figure 8-8 Age spectra and isochron plots of sample KL32-8 455.9m (muscovite)

Muscovite from sample KL32-8 455.9m yields a nearly flat age spectrum (a). A weighted mean age of $3.18 \pm 0.02 \text{ Ma}$ calculated from heating steps D-G contains ~67% of the ^{39}Ar released and has an acceptable MSWD. The rise in apparent ages displayed in the last ~10% of the age spectrum correlated with a drop in both K/Ca and radiogenic yield is probably due to high Ca inclusions such as sphene or apatite. An inverse isochron (b) of steps B-J reveals an apparent age of $3.18 \pm 0.16 \text{ Ma}$ with an $^{40}\text{Ar}/^{36}\text{Ar}$ intercept (293 ± 20) that agrees within error to the atmospheric ratio and has an acceptable MSWD value of 4.2. Figure and discussion reproduced from Peters (pers comm.) (see Appendix VIII).

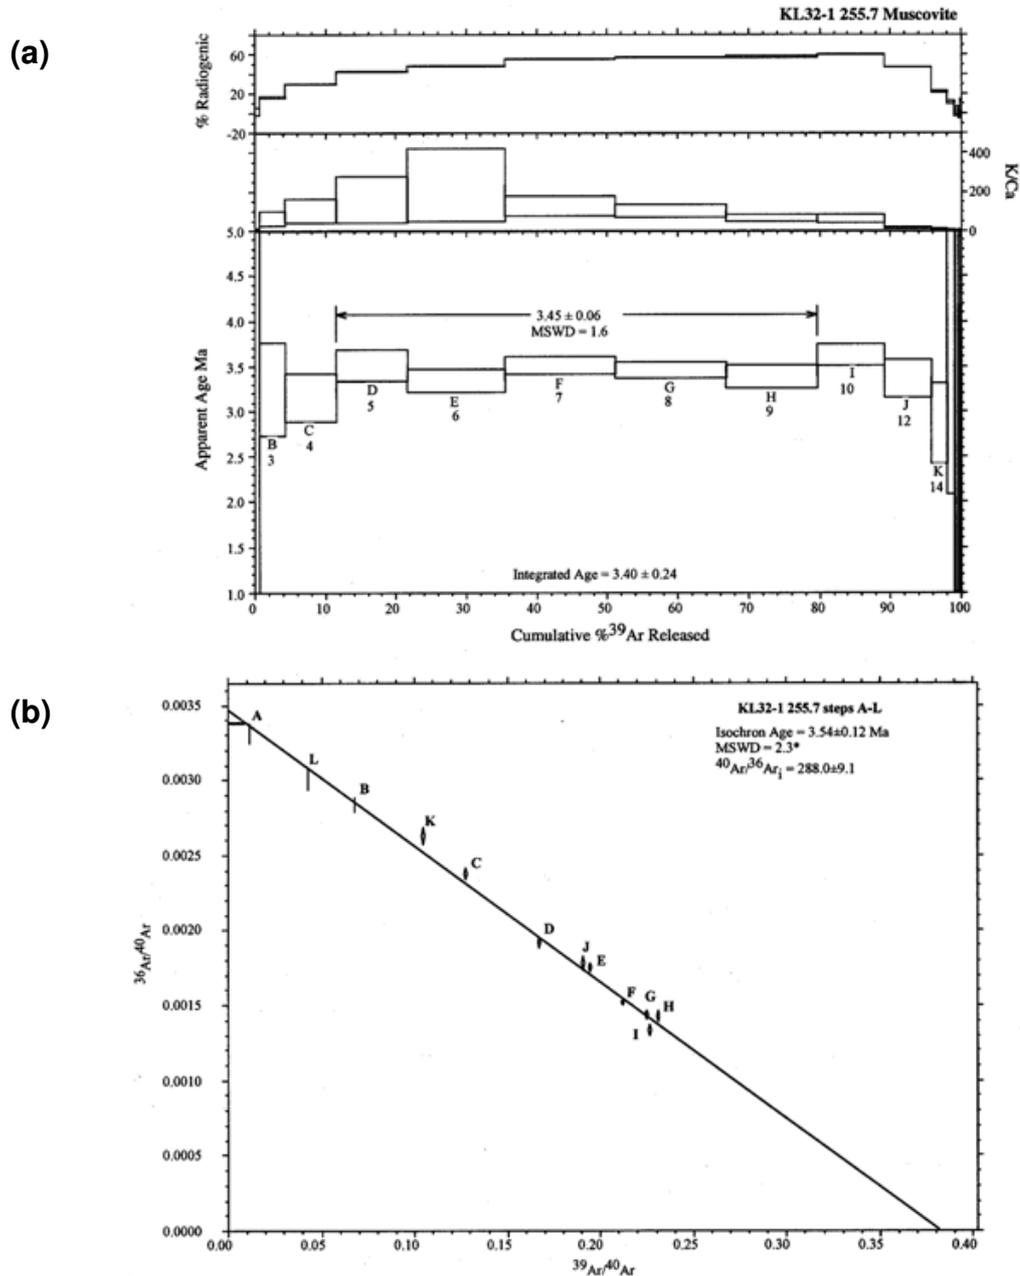


Figure 8-9 Age spectra and isochron plots of sample KL32-1 255.7m (muscovite)

The slight downward curve of steps E-H is suggestive of excess ^{40}Ar . Muscovite from sample KL32-1 255.7m yields a slightly hump-shaped age spectrum. A weighted mean age of $3.45 \pm 0.06\text{Ma}$ with an acceptable MSWD value is calculated for heating steps D-H. The inverse isochron reveals an $^{40}\text{Ar}/^{36}\text{Ar}$ intercept (288.1 ± 9.1) that agrees within error to atmosphere.

Table 8-1 Ages and precisions for $^{40}\text{Ar}/^{39}\text{Ar}$ methods on selected minerals

Sample	Mineral	Lithology	Plateau			Isochron		
			Age (Ma)	MSWD	error (Ma)	Age (Ma)	error (Ma)	MSWD
KL28-1 360.3m	Phlogopite	Fault	3.41		0.04	3.42*	0.04	1.7
KL32-8 331.0m	Phlogopite	Limestone	3.27	1.5	0.03	3.28	0.04	1.6
KL32-5 539.6m	Biotite	Fault	3.34	1.5	0.02	3.28*	0.04	1.0
KL32-5 652.4m	Biotite	Shale	3.23	3.0	0.04	3.20*	0.04	4.7
KL20-9 465.3m	Biotite	Shale	3.18*	0.5	0.02	3.19	0.03	3.0
KL32-8 455.9m	Muscovite	Shale	3.18*	0.42	0.02	3.18	0.16	4.2
KL32-1 255.7m	Muscovite	Fault	3.45*	1.6	0.06	3.54	0.12	2.3

Both plateau and isochron age dates are shown for each mineral for comparative purposes. The age attributed to each sample by Peters (pers comm.) has been marked by an asterisk (see caption discussions of Figure 8-3 to Figure 8-9). Note that only sample KL32-8 331.0m does not have good agreement between plateau and isochron ages. As such Peters (pers comm.) has attributed a weighted mean age of $3.28 \pm 0.02\text{Ma}$ to this sample (see Figure 8-4 and Appendix VIII).

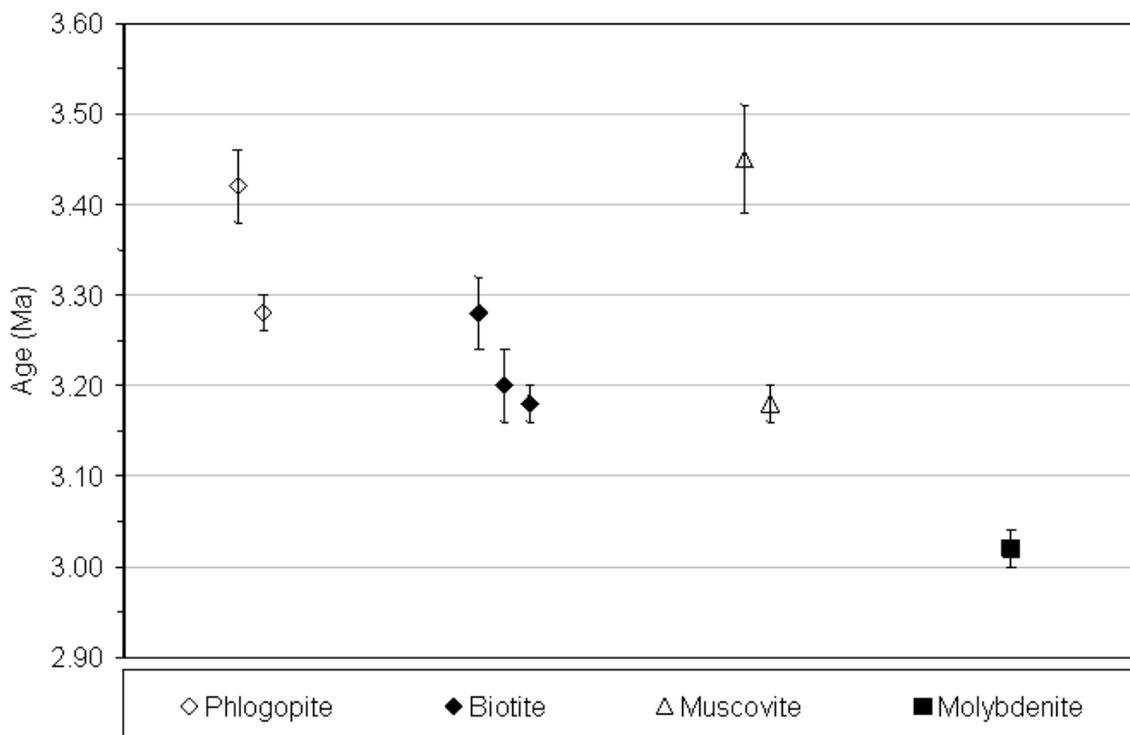


Figure 8-10 Absolute ages of hydrothermal minerals and their accuracies

Mineral phases are grouped into paragenetic sub-stages and placed in order from left to right.

8.3 INTERPRETATION OF AGE DATA

Geochronology has been used to confirm and calibrate the relative sequence of minerals established from visual examination.

Interpretation of Kucing Liar age data

$^{40}\text{Ar}/^{39}\text{Ar}$ ages in general represent the time when argon exchange between mineral and surrounding rock ceased. As such, this time may represent either:

1. crystallisation
2. resetting of the potassium-argon system by some event after mineral formation
3. closure to argon diffusion after slow cooling from crystallisation temperature to closure temperature (Snee et al., 1988).

The spectra recorded from results of this study all appear undisturbed and do not record any significant overprinting, resetting or disturbances in the argon gas emissions (e.g. Richards and Noble, 1998) from the sample, though several samples have small indications of excess ^{40}Ar (see Appendix VIII). Hence, the ages reported for Kucing Liar samples are interpreted to represent the age of crystallisation of the mineral as there is no disruption of the age spectra and, the shallow depth of the Kucing Liar system would not be conducive to slow cooling which precludes any of the ages being a closure age for argon diffusion (closure temperatures for argon diffusion are reported as 300-350°C for biotite (significantly higher for phlogopite) and 350-400°C for muscovite (Peters, 2001)). While the results derived from $^{40}\text{Ar}/^{39}\text{Ar}$ geochronology indicate that analyses represent ages of crystallisation, the tendency for older ages to have lower precision could indicate an extended period where the temperature was greater than the closure temperature. The large disparity in ages for muscovite is thought to be a function of grain size, which may cause recoil due to very fine grain size (Richards and Noble, 1998), supported by the apparent influence of excess ^{40}Ar (Appendix VIII). The problematical muscovite age derived from sample

KL32-1 255.7m (Figure 8-1) may be unreliable, as anomalously old ages have been reportedly derived from samples that have very fine grain size of 5-10 μ m (Richards and Noble, 1998).

It is not known when skarn alteration began. The two green phlogopite samples have two very different ages of 3.42 ± 0.04 Ma and 3.28 ± 0.02 Ma (Table 8-1), indicating a timespan of at least ~100ky when the hydrothermal system remained at temperatures $>350^{\circ}$ C, the closure temperature for phlogopite. Two samples of biotite infill have identical ages of 3.20 ± 0.04 Ma and 3.18 ± 0.02 Ma. The age dates for phlogopite and biotite indicate that the potassic alteration assemblage K-feldspar \pm biotite began at 3.28 ± 0.02 Ma and continued to 3.18 ± 0.02 Ma. The rapid age transition for potassic alteration relative to the older phlogopite samples may indicate a more rapid transition through the closure temperatures of phlogopite and biotite. A single muscovite sample with an age of 3.18 ± 0.02 Ma provides an oldest age for the zoned quartz-pyrite alteration, which is within error of the potassic group biotite ages. However, a second, potentially unreliable age for muscovite is older at 3.45 ± 0.06 Ma and apparently contemporaneous with early skarn alteration. An age for molybdenite post-dating covellite has been determined from Re-Os techniques as 3.02 ± 0.02 Ma (Mathur, pers comm.), which is the average of two analyses from the same sample as presented in Mathur *et al.* (2005). The two analyses of covellite-pyrite mineralisation from Kucing Liar have ages of 3.01 ± 0.02 Ma and 3.03 ± 0.02 Ma in Mathur *et al.*, (2005) are from the sample KL42-2 440.5m and are given geological and paragenetic context here. These ages suggest that quartz-pyrite alteration took no longer than 200ky.

Geochronology of the Ertsberg Mining District

Ages derived from magmatic biotite collected from intrusive bodies demonstrate a distinct period of magmatic activity between ~4.5 and ~2.5Ma (Table 8-3). The oldest intrusive rock is the Kay intrusion, situated between the Kucing Liar and Big Gossan deposits, at 4.44 ± 0.1 Ma and the youngest is a component of the Ertsberg intrusion at 2.65 ± 0.12 Ma. Ertsberg ages (~3.09-2.65Ma) overlap with the younger part of the total range of Grasberg ages (~3.33-2.77Ma). The Karume intrusion, situated between the two, has an age 3.13 ± 0.09 Ma, overlaps with ages from

both the Grasberg and Ertsberg igneous suites (Table 8-3). The single date of $3.51 \pm 0.02\text{Ma}$ from the Lembah Tembaga porphyry is contemporaneous with a date from the Wanagon sill ($3.46 \pm 0.06\text{Ma}$). A second age from the Wanagon body is older at $3.81 \pm 0.06\text{Ma}$. The North Grasberg intrusion also has two inconsistent ages; the older age of $3.5 \pm 0.23\text{Ma}$ overlaps with ages from Lembah Tembaga and Wanagon, while the younger age of $3.04 \pm 0.14\text{Ma}$ coincides with the middle of range from the Grasberg suite (Table 8-3).

Ages for alteration minerals in the two complexes display a continuum of hydrothermal activity, though the Ertsberg Igneous Suite was mineralised significantly later than Grasberg as deduced from Re-Os dating of sulphide material, which indicates younger ages for Ertsberg than Grasberg (Figure 8-11). An oldest constraint on Grasberg copper mineralisation of $3.07 \pm 0.01\text{Ma}$ is proposed based on $^{40}\text{Ar}/^{39}\text{Ar}$ geochronology of coarse brown phlogopite immediately preceding chalcopyrite mineralisation in the paragenesis (Pollard and Taylor, 2001). A younger age of $2.9 \pm 0.3\text{Ma}$ is provided for Grasberg copper mineralisation based on a Re-Os isochron age (Mathur *et al.*, 2000). An $^{39}\text{Ar}/^{39}\text{Ar}$ age of $2.82 \pm 0.04\text{Ma}$ for phlogopite from Big Gossan (Prendergast *et al.*, 2005) indicates that this deposit is similar in age to the EESS, while an $^{40}\text{Ar}/^{39}\text{Ar}$ age of $3.62 \pm 0.06\text{Ma}$ for K-feldspar from Wanagon indicates that this deposit is older than Grasberg, implying that the pyrite-Au-As-Zn-Bi-Te is either a much later overprint related to EESS mineralisation, or that this type of mineralisation developed at two distinct periods.

Sillitoe (1994) suggests that the maximum timespan of a single hydrothermal system is 1Ma. The Kucing Liar system appears to be half that at 500ky, but was a single event within a period of regional igneous activity lasting 1.5 Ma. Two other major hydrothermal events are related to the Grasberg Igneous Complex and the Ertsberg Intrusive Suite. The Kucing Liar system may be partially related to the Grasberg system though mineralised assemblages have different ages. Porphyry emplacement appears to predate and be contemporaneous with hydrothermal alteration, while the Kucing Liar mineralisation is contemporaneous with early stages of silicate alteration but older than mineralisation assemblages at Grasberg.

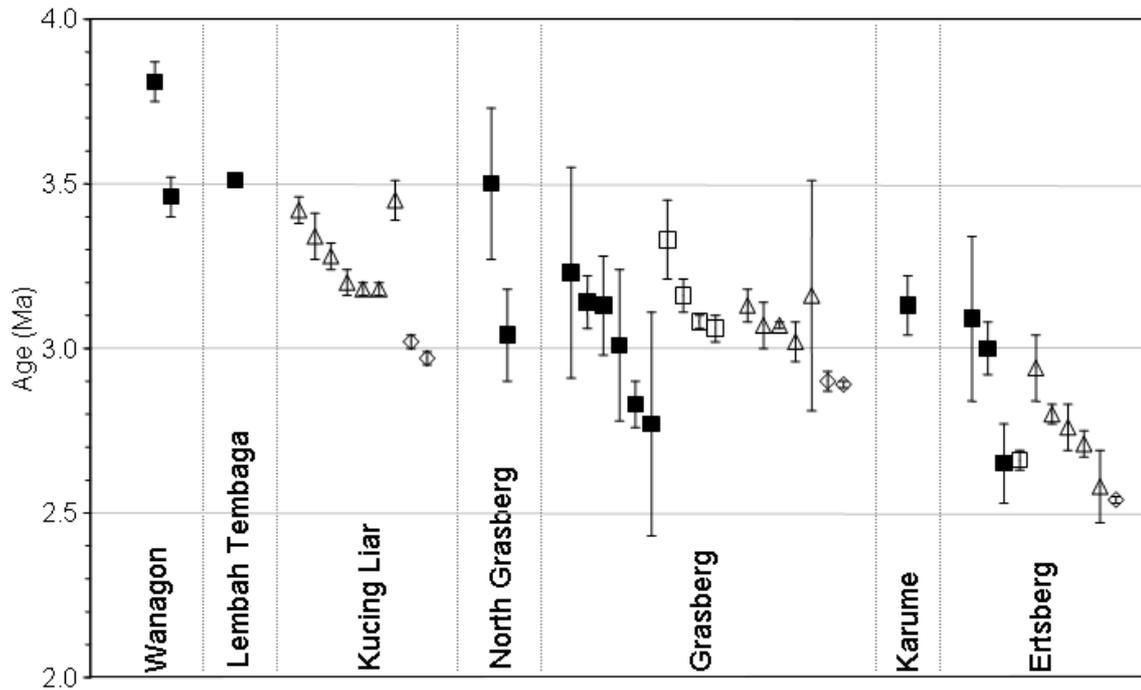


Figure 8-11 Geochronology of the Ertsberg Mining District

Ages of magmatic biotite and hydrothermal green phlogopite, brown phlogopite, muscovite and molybdenite samples collected in the district (this study (Chapter 2); McDowell et al., 1996; Pollard and Taylor, 2001 (Chapter 1)). Squares are magmatic ages, filled indicates a K-Ar ages while open indicate ^{40}Ar - ^{39}Ar ages. Triangles are hydrothermal minerals, all of which are ^{40}Ar - ^{39}Ar ages. Diamonds are Re-Os ages for sulphides. Kucing Liar ages are presented in paragenetic sequence, while all other samples are organised by spatial association and age.

Table 8-2 Geochronology of Ertsberg Mining District hydrothermal minerals

Sample	System	Method	Mineral	Age (Ma)
A96-43-5 275.0m	Grasberg	^{40}Ar - ^{39}Ar	Muscovite	3.16 ± 0.35
A96-43-5 68.5m	Grasberg (Kali)	^{40}Ar - ^{39}Ar	Biotite	3.13 ± 0.05
A96-41-3 92.5m	Grasberg	^{40}Ar - ^{39}Ar	Biotite	3.07 ± 0.01
A96-36-4 150.1m	Grasberg	^{40}Ar - ^{39}Ar	Biotite	3.02 ± 0.06
Unnamed	Grasberg	Re-Os	Molybdenite	2.90 ± 0.30
Unnamed	Grasberg	Re-Os	Sulphides	2.89 ± 0.10
B42 DOZ	Ertsberg East	^{40}Ar - ^{39}Ar	Phlogopite	2.94 ± 0.10
B43 GBT-A	Ertsberg East	^{40}Ar - ^{39}Ar	Phlogopite	2.80 ± 0.03
B41 DOZ	Ertsberg East	^{40}Ar - ^{39}Ar	Phlogopite	2.76 ± 0.07
DZ5-04 290.2m	Ertsberg East	^{40}Ar - ^{39}Ar	Biotite	2.71 ± 0.04
Unnamed	Ertsberg East	Re-Os	Molybdenite	2.54 ± 0.10

Sources of data: Pollard et al. (2001) and Mathur et al. (2005)

Table 8-3 Geochronology of Ertzberg Mining District intrusions

Sample	System	Method	Mineral	Age (Ma)
1001	Ertzberg East	K-Ar	Biotite	3.00 ± 0.08
1002	Ertzberg East	K-Ar	Biotite	2.65 ± 0.12
1003	Ertzberg East	K-Ar	Biotite	3.09 ± 0.25
DZ5-06 269.3m	Ertzberg East	⁴⁰ Ar- ³⁹ Ar	Biotite	2.66 ± 0.03
2001	Grasberg	K-Ar	Biotite	2.83 ± 0.07
2002	Grasberg	K-Ar	Biotite	2.77 ± 0.34
2003	Grasberg	K-Ar	Biotite	3.01 ± 0.23
2004	Grasberg	K-Ar	Biotite	3.14 ± 0.08
2005	Grasberg	K-Ar	Biotite	3.13 ± 0.15
2006	Grasberg	K-Ar	Biotite	3.23 ± 0.32
A96-40-5 95.0m	Grasberg	⁴⁰ Ar- ³⁹ Ar	Biotite	3.33 ± 0.12
A96-41-2 172.5	Grasberg	⁴⁰ Ar- ³⁹ Ar	Biotite	3.06 ± 0.04
A96-43-5 57.3m	Grasberg (Kali)	⁴⁰ Ar- ³⁹ Ar	Biotite	3.16 ± 0.05
3001	North Grasberg	K-Ar	Biotite	3.50 ± 0.23
3002	North Grasberg	K-Ar	Biotite	3.04 ± 0.14
LT 1-5 953m	Lembah Tembaga	⁴⁰ Ar- ³⁹ Ar	Biotite	3.51 ± 0.02
4001	Wanagon	K-Ar	Biotite	3.81 ± 0.06
4002	Wanagon	K-Ar	Biotite	3.46 ± 0.06
5001	Karume	K-Ar	Biotite	3.13 ± 0.09
6001	Kay	K-Ar	Biotite	4.44 ± 0.10

Sources of data: McDowell et al (1996) for K-Ar data, Pollard and Taylor (2001) for ⁴⁰Ar-³⁹Ar data. The Kali dyke sample from Grasberg is considered a younger age for the complex as they are the last intrusive phase.

9 Discussion

This discussion chapter aims to integrate the various results of the research program. Of interest in the first section is the nature of deformation and its relationship to tectonic forces, as well as the influence the deformation mechanism has on the emplacement of magmatic-hydrothermal systems. The second section intends to develop a model for the hydrothermal evolution, which is consistent with the results of fluid inclusion, stable isotope and metal distribution studies. These data indicate that zoned alteration mineralogy and base and precious metal mineralisation are related to phase separation and fluid mixing. The final section aims to compare and contrast the Kucing Liar genetic model with existing models of porphyry-epithermal mineralisation.

9.1 TECTONIC-MAGMATIC SETTING OF FLUID INFILTRATION

The major results that relate to tectonic models are the local structural setting and the geochronology of intrusive suites and spatially related hydrothermal systems. As limited data has been collected in relation to fault vectors, published literature concerning deformation mechanisms are used to review the results.

9.1.1 Tectonic transition and porphyry emplacement

The interpreted local tectonic history involves a change from folding and thrusting to more lateral fault displacement (Quarles van Ufford, 1996; Sapiie and Cloos, 2004). A change in deformation style can be brought about by a change in convergence direction of tectonic plates as shown by experiments for various collision angles at various obliquities (Casas *et al.*, 2001). A sharp contrast in deformation styles occurs at convergence angles between 15° and 30° (Figure 9-1). At angles $\leq 15^\circ$ strike-slip displacement occurred on 'R' and 'Y'-type shears and no significant uplift was observed, while for convergence angles $\geq 30^\circ$ an uplift zone bound by two fault zones formed. The strike-slip component of displacement decreased with increasing convergence angle, as did the number of 'R'-type faults. Arc-oblique 'P'-type orientations tend to dominate in the back limb of the uplifted zone and have been reproduced in experimental modelling of thrust environments. The change from reverse to strike-slip faults is caused by a change in convergence angle below 30° (Figure 9-1). Such change in convergence angle has been postulated for the development of New Guinea where southerly directions apparently changed to west southwesterly at ~5Ma (Sapiie and Cloos, 2004), immediately preceding igneous activity in the Ertzberg Mining District which persisted from 4-2Ma (Chapter 8).

Change in deformation styles from folding and reverse faulting to lateral fault movement may have driven fluid migration and could account for the temporal clustering of magmatic hydrothermal systems. The Idenberg Fault Zone was evidently active during fluid infiltration as revealed by the different offsets for stratigraphy and skarn (Chapter 4) as well as permeability

considerations which require continued generation of secondary porosity through fracturing to offset infilling of fractures with mineral growth (Cox et al., 2001). The expected stress differential and associated relaxation of confining pressures due to deformation changes arising from tectonic transitions could facilitate magma ascent (Tosdal and Richards, 2001), as well as causing fluid redistribution (Sibson, 2001). An association of porphyry emplacement with tectonic transition is consistent with general models for gold-producing porphyry episodes which are considered to be short-lived and commonly formed as an end-stage of arc development (Sillitoe, 1997).

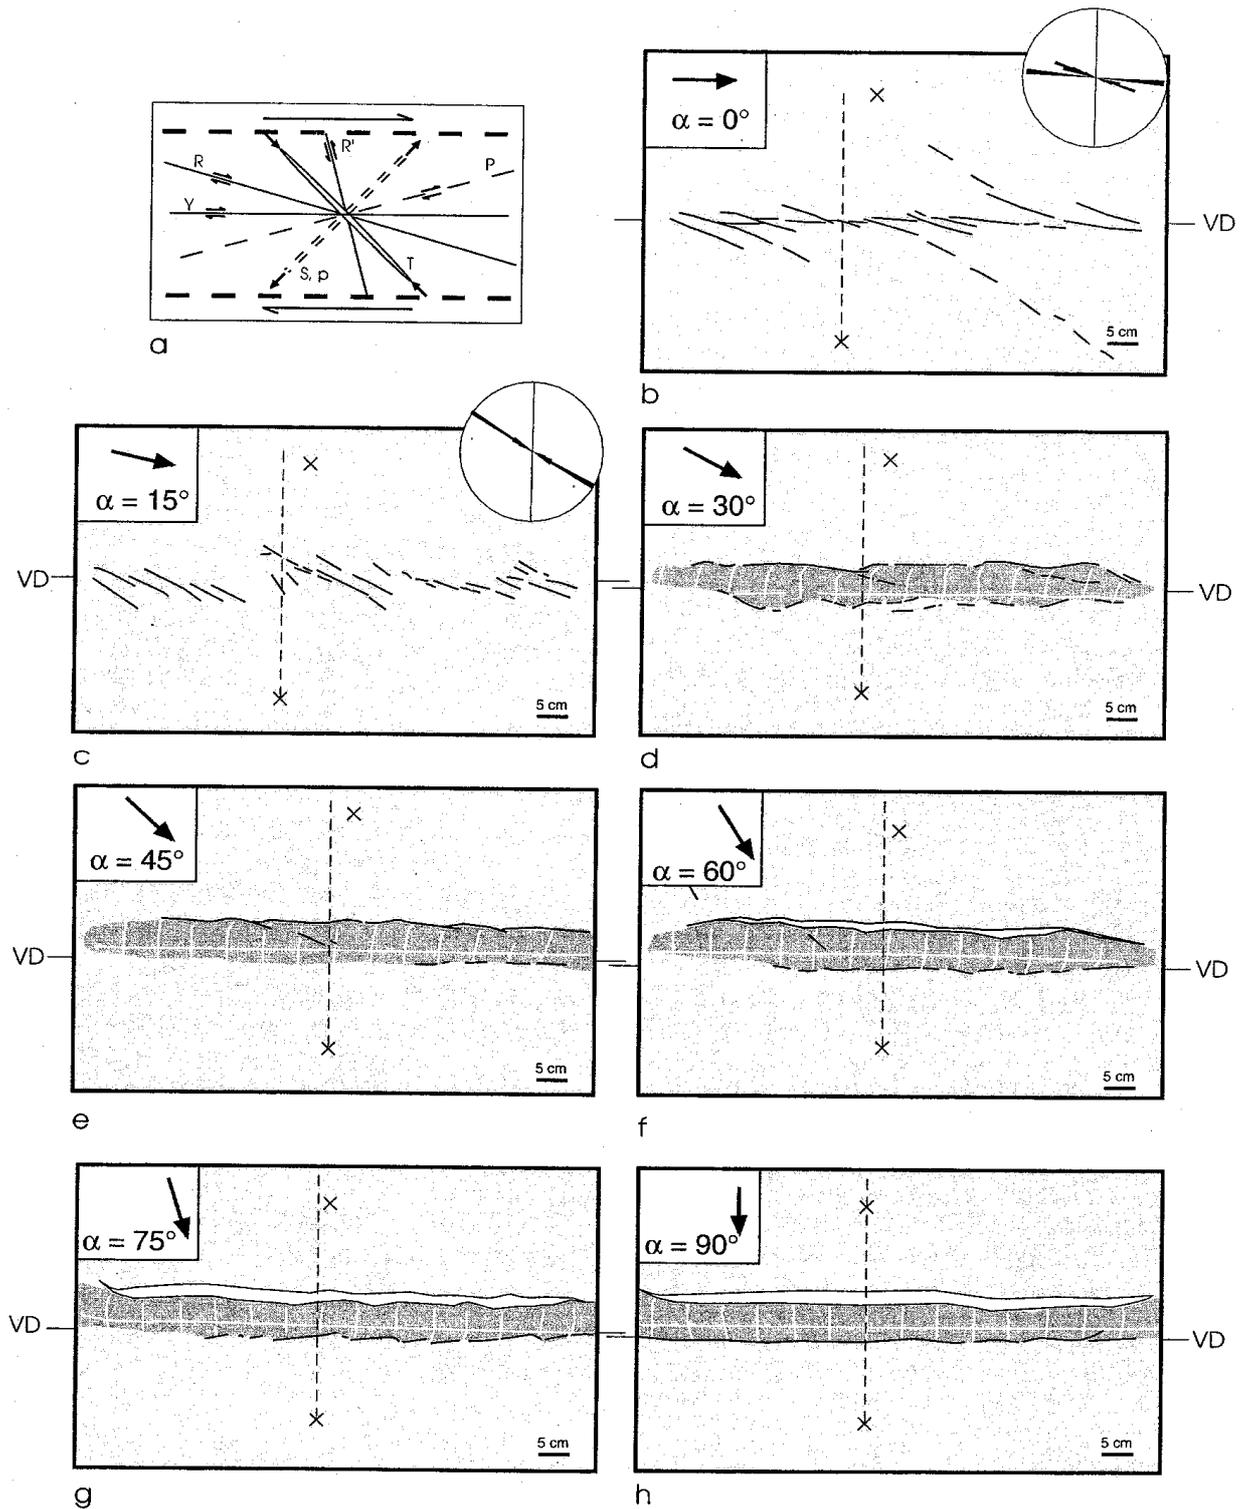


Figure 9-1 Analogue model of deformation front for various convergence angles

The figures range from pure strike-slip (a) to pure thrusting (h). The shadowed zones represent regions of uplift. The predominance of Reidel (R) structures for low convergence angles (α) is supported by models of strike-slip displacement (reproduced from Casas et al., 2001).

9.1.2 Progressive deformation and structural geometry

Kucing Liar is centred on the intersection between a complex fault zone and a heterogeneous litho-stratigraphic section containing sandstone, calcareous shale and thinly-bedded limestone. The main Kucing Liar mineralized zone lies in the Ekmai Limestone and the lower part of the Waripi Limestone where the sequence is displaced by the Idenberg Fault Zone. Minor alteration and mineralization (mainly covellite-bearing), is hosted by the upper sandstone member of the Waripi Limestone (Chapter 4). This stratigraphical control of ore deposition is repeated in other mineralized systems in the Ertzberg Mining District (Chapter 1). However, the localisation of hydrothermal systems requires both a primary fluid focus such as the Idenberg Fault Zone, as well as a favourable local environment of high permeability, such as the thinly-bedded limestone in the lower Waripi Limestone. Neither faults nor the units which act as a local host are uniformly mineralized, a combination of fault and stratigraphic control being required. Alteration and mineralization at the Nena deposit in Papua New Guinea are concentrated at the intersection of a vertical fault with a permeable coarse pyroclastic horizon (Bainbridge *et al.*, 1998). The Lepanto ore body in the Philippines occurs at the intersection of the Lepanto Fault and an unconformable contact between dacite and volcanoclastic rocks (Hedenquist *et al.*, 1998).

Fluid flow was focused along major stratigraphic contacts in stratabound breccias, probably produced by deformation of heterogeneous stratigraphy as well as where the favourable orientation of stratigraphic layering relative to fault movement resulted in tensional strain (Chapter 4). Fluid infiltration most likely occurred during active fault movement as indicated by continued development of new veins and fracture infill. The Idenberg Fault Zone is characterised by a number of internal offsets (Chapter 4) that have different asymmetry and resulted in >600m of vertical displacement based on the relative positions of distinctive marker horizons (Chapter 2). While there is enough evidence to indicate both reverse-slip and strike-slip movement in the Idenberg Fault Zone, it is unclear if it represents separate deformation episodes or was combined in an oblique-slip system. The development of offsets within the primary fault zone is the result of

progressive deformation and has resulted in the concentration of late stage hydrothermal activity (Chapter 4) including copper-gold mineralization (Chapter 5) within complex fault jogs. The Idenberg Fault Zone possesses two distinct offsets as defined by lithological distribution models (Chapter 4). The displacement of stratigraphy is evident by identification of marker horizons and record a relative vertical offset of ~600m. Skarn alteration is also displaced across the Idenberg Fault Zone although the stratigraphy on either side is altered at different stratigraphic levels (300m difference). Based on the assumption that alteration would occur at similar levels on either side of the fault zone in similar rock types, the difference between lithological and skarn displacement indicates skarn formed after substantial fault movement had already occurred.

Offsets or jogs in fault zones are either dilatant or compressional structures (Sibson, 1989) depending on their orientation and the direction of movement. The visible displacement of key marker horizons within the Kucing Liar stratigraphy suggests the Idenberg Fault Zone is a steep reverse fault. However, lateral movement for the Idenberg Fault Zone could also account for the apparent vertical displacement of stratigraphy. For instance, left-lateral movement of stratigraphy folded about a west-northwest plunging fold axis, such as occurs in the Yellow Valley Syncline, would result in apparent north side up vertical displacement. Fault offsets or jogs may form from the intersection of and incorporation of older structures with younger structures (e.g. Hildenbrand et al., 2000), or from progressive deformation (Dube and Guha, 1992). The offset within the Idenberg Fault Zone may represent two periods of faulting in which an early wide vertical fault has been intersected and offset by northeast dipping structures. If this were the case, another wide subvertical fault segment should be present at deeper levels on the southwestern side of the fault zone. Due to complex lithological relationships combined with low data density, the existence of a fault at this location is not ruled out. A second option for explaining the Idenberg Fault Zone geometry is that the pattern of narrow and wide structures is the result of progressive deformation. A left-lateral strike-slip history involving an early dilational jog followed by a later compressional jog would be consistent with published deformation models. Experimental studies of continuously deforming fault zones (Tchalenko, 1970; Dube and Guha, 1992) indicate an evolution of fault

structure from:

1. low angle tensional ('R'-type) structures forming at peak shear resistance in dilational orientations accompanied by a conjugate high angle fractures ('R1'-type) that are also dilational
2. oblique restraining, or compressional ('P'-type) shears form following peak shear strength in an asymmetric orientation to the R-type fractures, and finally,
3. throughgoing ('D'- or 'Y'-type) fault structures (Figure 9-4).

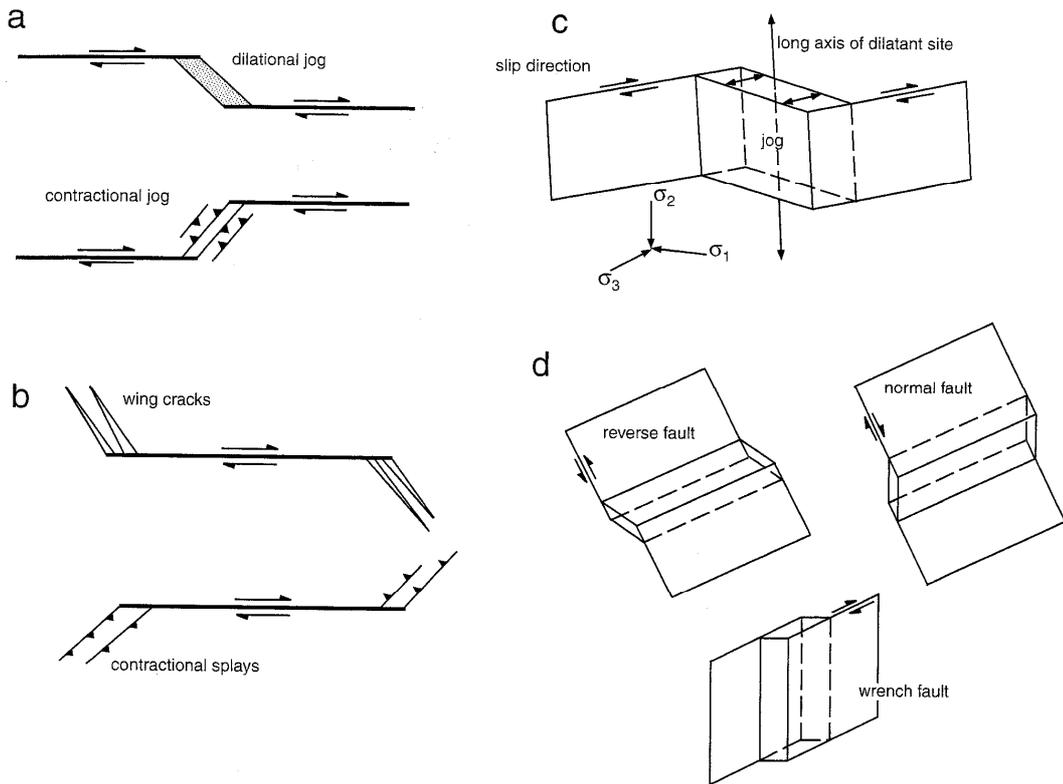


Figure 9-2 Geometry and structural detail of fault jogs

(a) Geometry of contractional and dilatant jogs. (b) Wing cracks and contractional splays developed around fault terminations (c) Geometry of a dilatant jog relative to fault slip direction (d) Orientation of jogs in contractional, extensional and lateral movement vectors. Figure reproduced from Cox et al., (2001). Note that the Idenberg Fault Zone is very similar in geometry to the normal fault geometry, however, this relationship is ruled out due to inconsistency with the only possible movement vectors which are reverse and left-lateral.

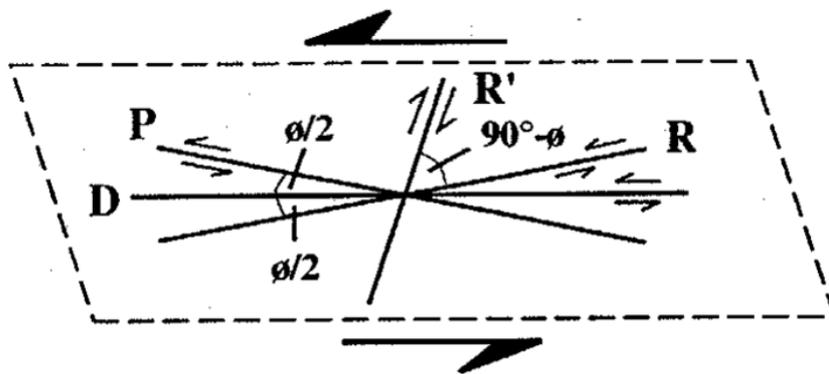


Figure 9-3 Naming convention for structures present in a left lateral fault-slip system

Adapted from Tchalenko (1970)


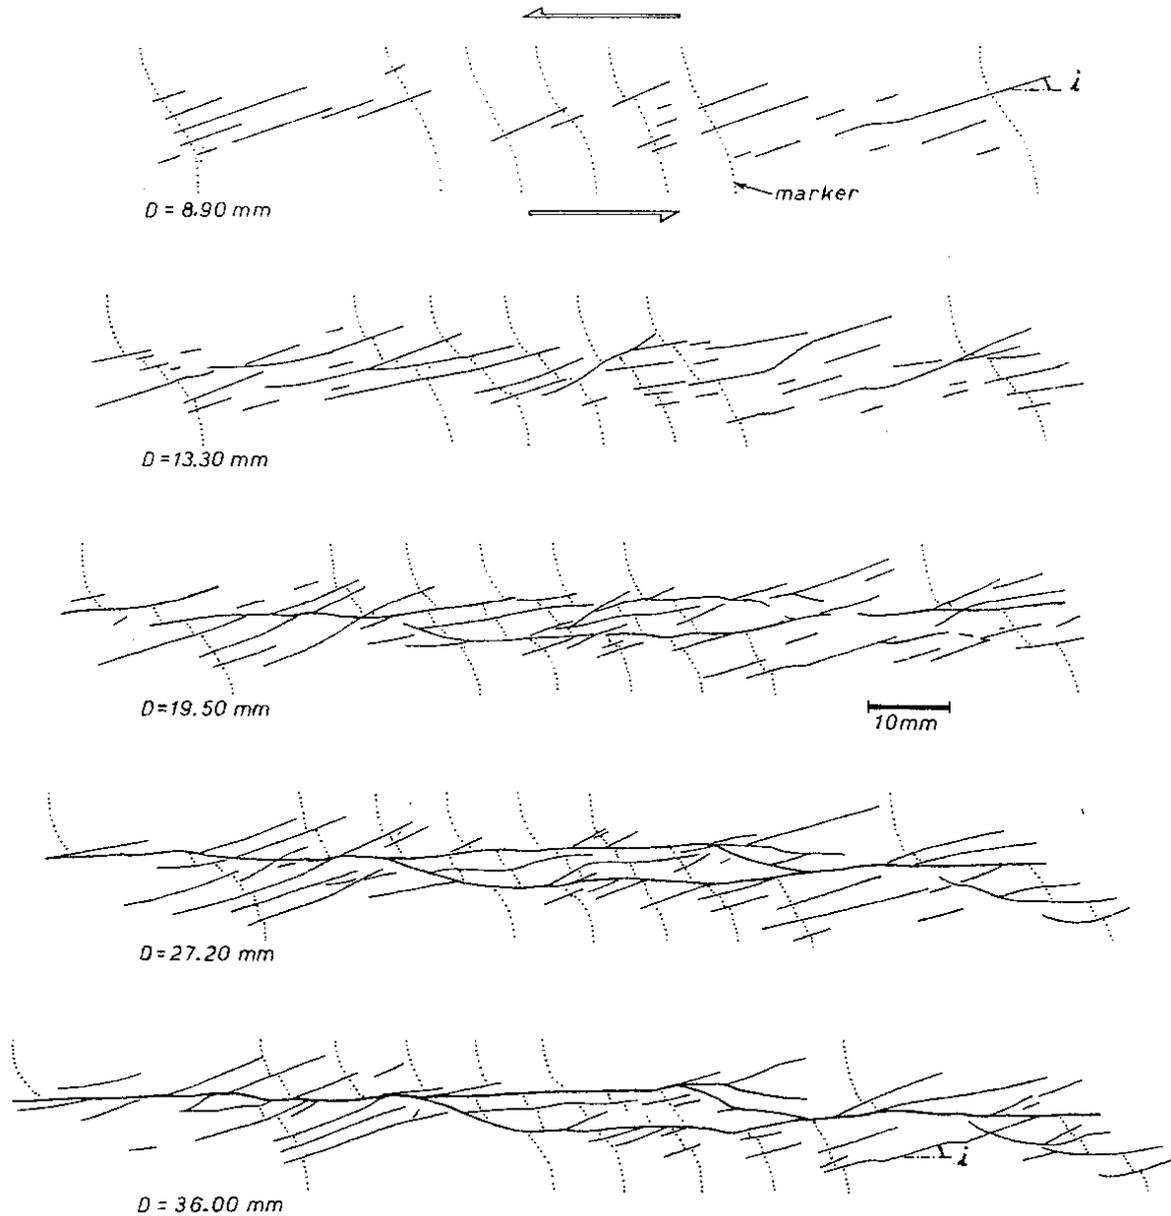



Figure 9-4 Geometric characteristics of strike-slip faults

Progression of deformation features produced in experiments of left-lateral fault displacement. D =distance of displacement. Reproduced from Tchalenko (1970).


Figure 9-5 Speculative models for development of structural offset in Idenberg Fault Zone

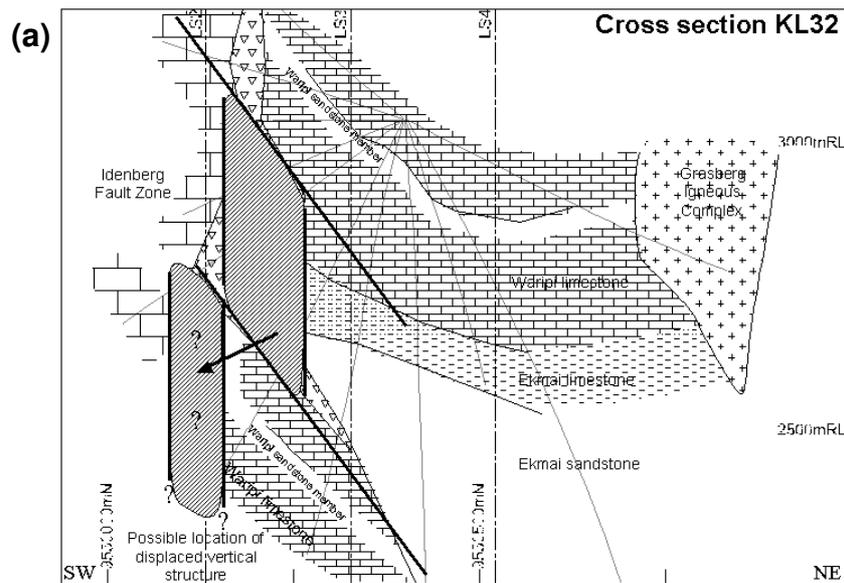

Three alternatives for the development of offsets in the Idenberg Fault Zone. (a) A model of two-phase faulting where an early near-vertical fault is overprinted and offset by steeply dipping faults. The lack of data in the expected location of the displaced fault zone means that this model is not precluded. (b) A

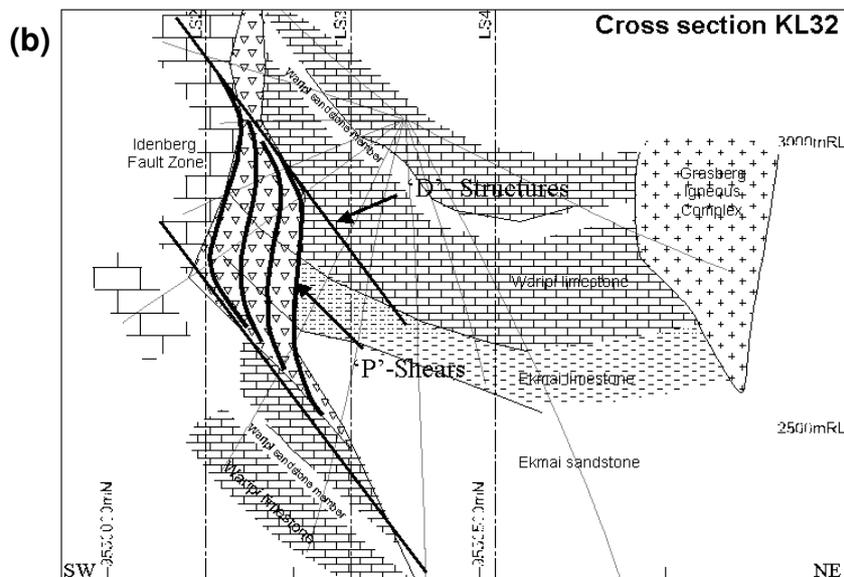

compressional or contractional offset where progressive deformation of a steeply-dipping fault zone results in a stepover between parallel fault structures. The model implies that each line through the offset is a small thrust-fault. These types of structures will eventually seize up and progress to throughgoing structures (c)

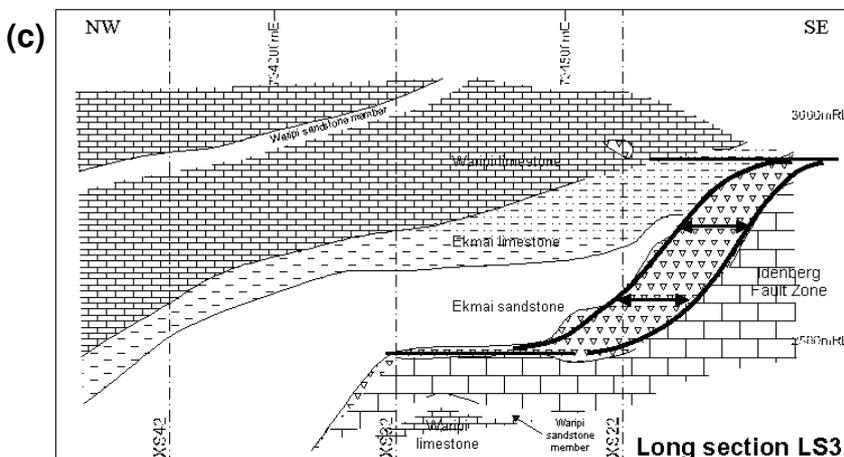

The small offset visible in long section must be a dilational offset whether produced during vertical or left lateral movement. The lack of later paragenetic minerals in this offset suggests it formed during vertical displacement. This is supported by the association of early garnet with this structure.

9.2 FLUID EVOLUTION LEADING TO HYDROTHERMAL MINERALIZATION

The Kucing Liar deposit is associated with a complex alteration succession which includes some 26 major minerals in distinct assemblages (Chapter 2). The hydrothermal minerals can be divided into four distinct groups which include:

- prograde and retrograde calcic and magnesian skarn
- potassic-magnetite alteration plus retrograde skarn
- silicification \pm muscovite and anhydrite alteration
- sulphide mineralization, including chalcopyrite or covellite \pm pyrite zones plus galena-sphalerite

The relationship of prograde skarn in limestone and hornfels development in shale is unclear. Both exhibit a similar early paragenetic history where clinopyroxene \pm garnet is overprinted by K-feldspar \pm biotite (Chapter 2). Timing relationships between the two copper-bearing sulphides and pyrite indicate that they must be near-contemporaneous (Chapter 2), which supports the observed metal zoning. Overprinting of an early chalcopyrite-bearing mineralized zone by later covellite-bearing mineralization should produce a new metal zonation, or at least some interference patterns, but none is observed (Chapter 5).

9.2.1 The collapse of magmatic-hydrothermal systems


The hydrothermal mineral paragenesis records a decrease in temperature conditions, from $>600^{\circ}\text{C}$ to $<400^{\circ}\text{C}$, which may have been influenced by fluid mixing in the Idenberg Fault Zone. Fluid conditions for quartz alteration that overprints skarn and potassic alteration are well constrained by fluid inclusions in quartz which suggest temperatures of formation $<420^{\circ}\text{C}$. Quartz alteration also hosts lower temperature ($\sim 300^{\circ}\text{C}$) fluid inclusions though these are probably not related to primary growth and could be interpreted to represent later overprinting fluids. Temperatures $>400^{\circ}\text{C}$ at shallow depths mark the normal limit for the brittle behaviour of rock types (e.g. Meinert *et al.*, 2003). Ductile behaviour seals the system from significant interaction with local

waters (Fournier, 1996; Meinert *et al.*, 2003), while brittle conditions would be expected to promote infiltration by external fluids. This is in agreement with stable isotope data which record shifts toward lower $\delta^{18}\text{O}_{\text{FLUID}}$ values during retrograde skarn and quartz alteration (Chapter 8).


The water associated with skarn and potassic alteration was clearly magmatic (Chapter 8), while later quartz and anhydrite alteration were caused by distinctly lower $\delta^{18}\text{O}$ fluids which are believed to have been close to local meteoric water (Chapter 8). Quartz alteration is closely associated with the Idenberg Fault Zone, and this association may indicate that structural evolution was a driving force behind fluid mixing and dilution. Fluid dilution in the Idenberg Fault Zone may also have been promoted by phase separation of magmatic fluids. Phase separation may occur during sudden pressure drops such as massive hydrofracturing, sudden removal of lithostatic load (sector collapse of a volcanic edifice), or rupturing at the brittle-ductile transition (Fournier, 1999). If phase separation of hydrothermal fluids did occur at Kucing Liar, it was probably a consequence of the low hydrostatic pressures in the Idenberg Fault Zone during active deformation. Hypersaline fluids, such as those generated by phase separation and that produced quartz alteration, may not pass across the ductile-brittle boundary, due to their high density and viscosity (Hedenquist *et al.*, 1998). However, the ductile-brittle boundary is permeable to buoyant, low-salinity and low-viscosity vapour, as evidenced from passive degassing in volcanoes unassociated with eruptive events (Hedenquist *et al.*, 1998).

9.2.2 Effect of fluid mixing on ore chemistry

The combination of lower temperatures and increased external fluid input is expected to have had a significant impact on the hydrothermal chemistry, resulting in conditions favourable for sulphide deposition and high sulphidation mineralization. A higher degree of local water interaction is believed to have promoted quartz precipitation below 420°C from highly mixed waters the Idenberg Fault Zone. The effect of reduced temperatures in the system was probably to promote hydrolysis-disproportionation of SO_2 in the magmatic fluids, a process which occurs at ~400°C (e.g. Seedorff *et al.*, 2005). This process is a hydrolysis reaction defined as:




Anhydrite is derived from the reaction of sulphuric acid with calcium-bearing fluids which generate anhydrite via the reaction:



(Burnham, 1979). The effect of producing anhydrite is to generate hydrochloric acid which is involved in the formation of the assemblage quartz \pm muscovite from K-feldspar by the reaction:



The development of chalcopyrite and the accompanied sulphidation of magnetite are achieved via reactions:



Precipitation of base metals from brine is based on a H_2S interaction via similar reactions to that above. Advanced dilution would have exacerbated the H_2S development through continued cooling and availability of H_2O , resulting in the quartz-muscovite-anhydrite assemblage as well as driving metal precipitation from brines and sulphidation of magnetite to form extensive pyrite and chalcopyrite development. The development of the assemblage quartz \pm muscovite, anhydrite has been linked to the process of sulphur disproportionation (Burnham, 1979, Tosdal and Richards, 2001).

Low salinity magmatic fluids related to covellite mineralization were circulating at temperatures around 300°C (Chapter 6). Phase separation was probably limited to the quartz alteration process (Chapter 6), which in turn was closely associated with movement of the Idenberg Fault Zone

(Chapter 4) and related fluid mixing (Chapter 8). Therefore the origin of Au-As-(Sb-Hg) low sulphidation mineralization, which is concentrated at the upper zones of Kucing Liar, is believed to be related to the interaction between low density phases and local meteoric waters due to Idenberg Fault Zone movement. Extraction of a low-density magmatic phase may have preferentially partitioned Au, Sb and As as bisulphide complexes (Bessinger and Apps, 2003; Heinrich *et al.*, 2004). Interaction of this low density phase with local meteoric waters would have caused the “vapour” to contract to form a low salinity liquid, as preserved in fluid inclusions in fluorite related to covellite (Chapter 7). Heinrich *et al.*, (2004) have suggested that contracted magmatic vapour may be in equilibrium with muscovite. A model whereby low density vapours are contracted back to a liquid form following cooling due to contact with local meteoric water (*cf.* Mancano and Campbell, 1995) is consistent with the observed pattern of low salinity liquids related to covellite-bearing mineralization hosted in quartz alteration that previously developed from high density brines. The expected high-acidity fluid derived from mixing of magmatic vapour and meteoric water would form kaolinite, however, the carbonate wall rocks would have had a high capacity for acid buffering. The effectiveness of fluid mixing in the mineralization process is demonstrated by the almost total precipitation of saturated gold from magmatic brine that is diluted 10-fold with meteoric fluid containing negligible chloride (Gammons and Williams-Jones, 1997). Calculations also indicate that 99% of copper partitioned into the aqueous fluid precipitates as the fluid is cooled to 250°C, most between 350-250°C window, though copper does precipitate at higher temperatures from NaCl-saturated fluids derived from shallow, low pressure systems (Cline and Bodnar, 1991).

9.3 KUCING LIAR IN THE CONTINUUM OF PORPHYRY-RELATED ORE SYSTEMS

9.3.1 Classification of porphyry-epithermal ores

Porphyry-related ore deposits are a very common deposit throughout the Pacific Rim with numerous examples in New Guinea, the Philippines, the Rocky Mountains of Canada and USA, Central America, Peru and Chile. There are a number of classes that have distinct mineralization styles and gangue alteration assemblages that are all ascribed an origin related to porphyry magmas (Figure 9-6).

1. Porphyry-hosted mineralized systems are common with chalcopyrite \pm bornite hosted in quartz stockworks in potassic alteration zones
2. Skarn deposits are frequently found at the margins of the intrusive bodies and are divided into proximal and distal varieties
3. High sulphidation epithermal deposits are typically external to porphyry stocks and have typical assemblages of covellite, enargite, digenite, chalcocite related to advanced argillic alteration characterised by alunite, kaolinite and diaspore.
4. Base metal veins (Au-As-Sb \pm Ag-Zn-Pb) are common at more distal locations from the porphyry stocks where mineralization is related to locally massive sulphide deposition
5. Low sulphidation epithermal Au-Ag deposits are distal to hypothesized coeval porphyry stocks

Kucing Liar contains zones with characteristics similar to the first four of these styles that represent a chemically zoned system. The chalcopyrite (-magnetite) ores is typical of proximal Cu-Au skarns, whereas the quartz-muscovite-covellite is typical of high sulphidation epithermal in phyllic environments (Hedenquist *et al.*, 1997) and the locally massive pyrite bodies with

accompanying enargite and auriferous arsenian pyrite, possibly with tennantite are similar to descriptions of base metal veins such as is the major ore source at Butte, Montana (*cf.* Einaudi *et al.*, 2003). One abnormality is that high sulphidation mineralization at Kucing Liar is related to silica-pyrite-muscovite (phyllic) style alteration rather than advanced argillic alteration. This may be because the pH was not low enough to form kaolinite and alunite, most likely due to buffering by carbonate rocks. Alternatively, covellite \pm pyrite \pm enargite may have formed in equilibrium with muscovite. Heinrich *et al.*, (2004) have now suggested a process involving contraction of magmatic vapour which is predicted to be in equilibrium with muscovite. Muscovite-stable alteration at Lepanto-Far Southeast was associated with water cooler, and less saline than that responsible for only slightly older potassic alteration.

As the primary minerals of economic interest tend to be sulphides, discrimination of conditions tends to be based on the concept of sulphidation, or the oxidation state of the sulphur species. This condition will be based on both the fS_2 , fO_2 and temperature conditions (Figure 9-7). The porphyry skarn ore represented by chalcopyrite \pm bornite developed under low to intermediate sulphidation conditions, in contrast to those of the high sulphidation assemblage covellite \pm enargite (*cf.* Sillitoe and Hedenquist, 2003). Chalcopyrite precipitation at Bajo de la Alumbrera (Argentina) is constrained to a temperature window between 400-320°C (Ulrich *et al.*, 2001b) derived from Cu concentrations measured in fluid inclusions, and mineralization at Far Southeast is reported at ~500°C deposited from brines (Mancano and Campbell, 1995). The conditions of intermediate sulphidation are within chalcopyrite, tetrahedrite-tennantite and Fe-poor sphalerite stability, and sulphide assemblages lack appreciable arsenopyrite and pyrrhotite. Based on the environment and conditions, it appears that Kucing Liar is a combination of porphyry skarn chalcopyrite ores, high sulphidation covellite \pm enargite ores, and intermediate sulphidation base metal veins represented by auriferous arsenian pyrite and galena-sphalerite ores.

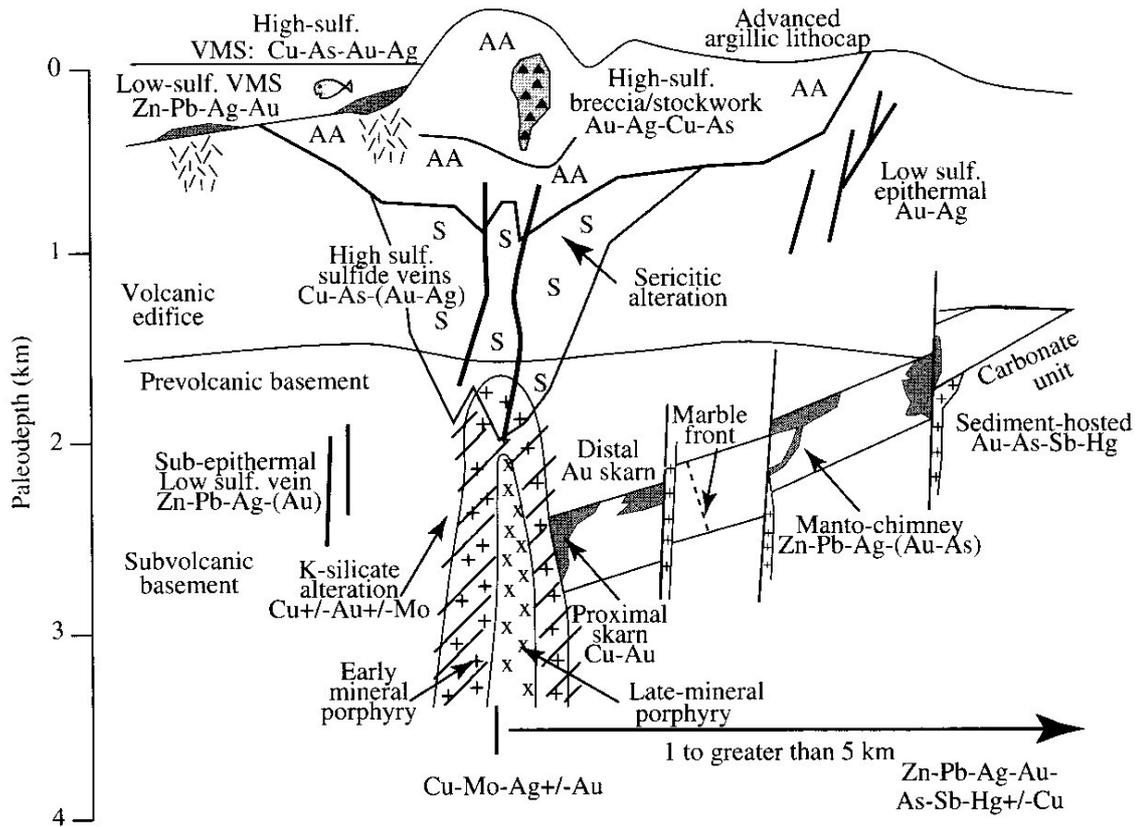


Figure 9-6 Generalised model of porphyry-related ore systems

In this model porphyry and skarn are transitional while porphyry and epithermal styles of mineralization will be distinct. It is tempting to assume from its location that Kucing Liar represents a proximal skarn at the margin of the Grasberg Igneous Complex as indicated in Figure 9-6. However, covellite-bearing mineralization at Kucing Liar preceded chalcopyrite ± pyrite ± bornite mineralization in the GIC, as constrained by biotite age of 2.94 ± 0.02 (Pollard et al., 2006). Although Kucing Liar predates the main phase of Grasberg mineralization (Chapter 8), it may actually be coeval with earlier phases of the Grasberg Igneous Complex (Macdonald and Arnold, 1989). Figure reproduced from Tosdal and Richards (2002).

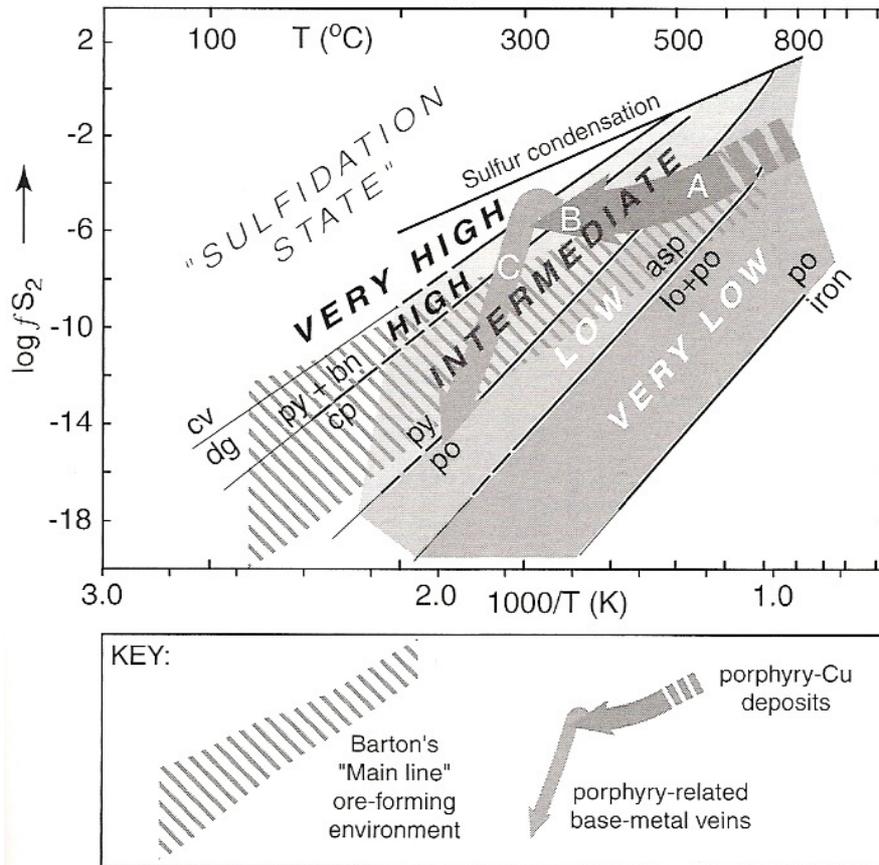


Figure 9-7 Plot of $\log f_{S_2}$ – Temperature for fluids in porphyry systems

This diagram is intended to illustrate the relationships between the various sulphidation states referred to within porphyry-related systems. It is apparent that sulphidation state is not directly analogous to the sulphur fugacity (f_{S_2}). The increase in sulphidation state with decreasing temperature at constant $\log f_{S_2}$ may be directly related to disproportionation of SO_2 , which occurs at temperatures $<400^\circ C$. The plot is considered relevant to Kucing Liar evolution as path A-B represents the progressive development of pyrrhotite-pyrite-chalcopyrite followed by pyrite \pm bornite and finally digenite-covellite \pm pyrite. The path B-C would represent a decrease in sulphidation state due to dilution in external water. Some fluids within Kucing Liar continued along a constant $\log f_{S_2}$ from point B as evidenced by the precipitation of native sulphur in some zones of covellite mineralization. Figure reproduced from Einaudi et al. (2003).

9.3.2 Juxtaposition of porphyry-epithermal systems

Porphyry-(skarn) and epithermal mineralization may be juxtaposed by overprinting of a later system due to withdrawal of the magma chamber, or by telescoping of the same process through uplift and denudation (Figure 9-8). Padilla-Garza et al. (2001) propose such a model for the Escondida copper deposit where advanced argillic alteration and high sulphidation mineralization postdate the main stage potassic-style alteration by 3Ma. The Agua Rica deposit in Argentina

resembles Kucing Liar in the sense that early porphyry-style alteration and mineralization is juxtaposed with high sulphidation mineralization (Landtwing et al., 2002). However, in this case Landtwing et al. (2002) proposed that the superposition of the different styles of mineralization resulted from a protracted magmatic-hydrothermal history. This is also the case at the Collahuasi district in northern Chile (Masterman et al., 2005) where it is proposed that at least 1km of denudation occurred over 1.8Myr between formation of early porphyry-style alteration at the Rosario deposit and mineralization and high sulphidation mineralisation and related advanced argillic and phyllic alteration zones. The porphyry-epithermal transition may be the result of rapid uplift and denudation (Sillitoe, 1999), a condition that is likely during convergence tectonics giving rise to volcanic activity. In this process, epithermal mineralization is not the result of a later hydrothermal system but is generated due to rapidly changing conditions during a single hydrothermal event. Such a dramatic change in conditions may be the result of volcanic processes and involve catastrophic unloading due to collapse of the volcano (e.g. van Wyk de Vries *et al.*, 2000), as is believed to have produced the large Ladolam Au resource within the Luise caldera in the Lihir Island Group. However, at Lihir, the porphyry system is dated at ~1Ma, while the mineralized epithermal system is dated to 250ky and the current geothermal system is no older than 100ky. The differences in these ages are similar to those between the different mineralized systems in the Ertsberg Mining District, indicating that they may have been sourced from different magma generations.

Based on the uplift of 1mm/yr discussed in Chapter 8, 0.5km of uplift may have taken place during the life of the Kucing Liar hydrothermal system. The transition from potassic alteration to phyllic + quartz alteration occurred within a 40ky period (Chapter 9), precluding any telescoping due to denudation in that time. Sector collapse is not ruled out though there is no hard evidence for this process. The process most likely to have caused the observed development of chalcopyrite and covellite-dominant mineralized zones at Kucing Liar is believed to be chemical changes in hydrothermal fluids (Figure 9-7). The relative sulphidation state of mineralising fluids will be controlled by interaction with external water that caused reduction of magmatic SO₂ (see Section

9.1). Figure 9-7 indicates that the mineralization in Kucing Liar may represent the transition to high sulphidation (chalcopyrite \rightarrow covellite) and back to low sulphidation (such as the auriferous arsenian pyrite) due to addition of external water, which drives fS_2 lower. The lack of variability of alteration and mineralization styles in some deposits may indicate a lack of fluid mixing, or too much mixing. The sulphur budget of a hydrothermal solution cannot be changed without external influence. Disproportionation of SO_2 would not in itself change the sulphur content, but would drive the system towards high sulphidation states at lower temperatures (Figure 9-7). A steady addition of water would lower relative sulphur content thereby maintaining a constant sulphidation state. Thus, in the case of Kucing Liar, sealing off the Idenberg Fault Zone would control the fS_2 while fluids that escaped into the overlying rock mass would come into contact with meteoric water and have their sulphur content diluted.

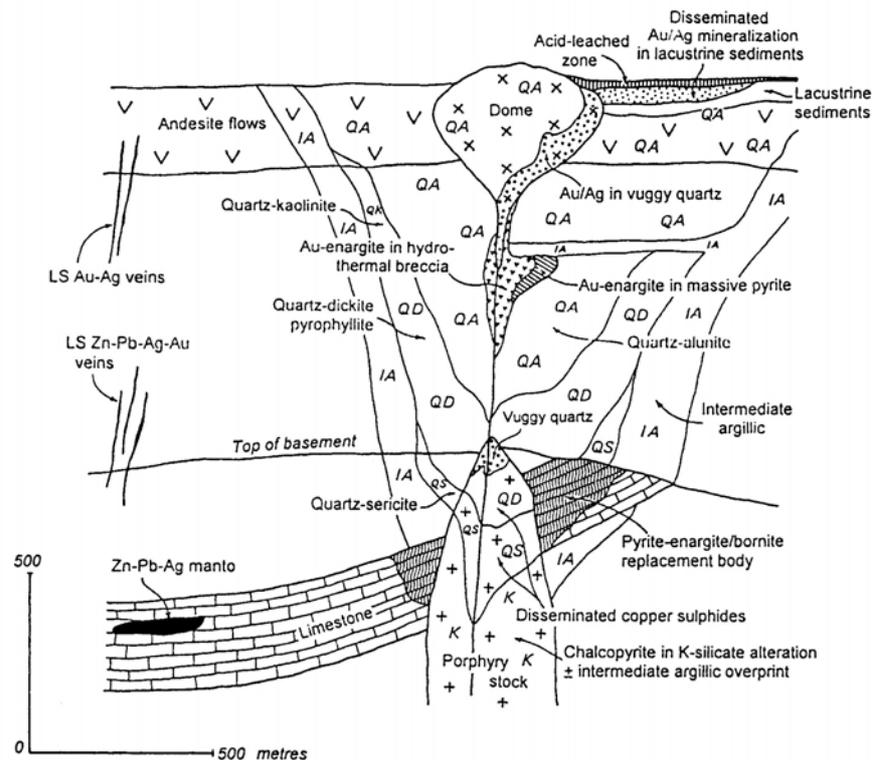


Figure 9-8 Telescoping of epithermal systems into porphyry environment

This figure illustrates how high sulphidation pyrite-enargite with associated quartz-muscovite alteration can be juxtaposed against a porphyry intrusion and its proximal skarn zone. This model requires some time lapse between skarn formation and high sulphidation mineralization. Figure reproduced from Sillitoe (1994).

9.4 CONCLUDING REMARKS

Kucing Liar holds evidence that porphyry-related deposits are mineralogically and metallogenically zoned and that transitions from one style to the next can be relatively rapid, as seen from the near contemporaneous development of potassic and overprinting quartz-pyrite alteration zones. The results of this research have indicated that the range of porphyry-related deposits, skarn (calc-silicate-magnetite rocks), porphyry (potassic altered rocks), high sulphidation epithermal (quartz \pm covellite \pm pyrite), carbonate replacement (arsenian pyrite \pm chalcocopyrite \pm covellite) and low sulphidation epithermal (galena-sphalerite \pm Au-As-Sb) can form during a single prolonged hydrothermal event. The variations are due to varying degrees of fluid evolution related to cooling and dilution by local water and hence represent relative distance from source in terms of time, space and composition. Interactions with external waters are related to the brittle-ductile transition, which may cause phase separation in the hydrothermal fluid, segregating ore metals between chloride-dominant brines (Fe-Cu-Zn-Pb-Ag) and low density bisulphide-dominant phases (Au-As-Sb). The separation of low and high-density phases at the brittle-ductile transition is expected to facilitate cooling and dilution effects through interaction with local groundwaters. Fault movement localised the conditions required for hydrothermal fluid evolution, in particular the pressure. The study has shown that fault movement and the level of complexity inside the fault system facilitate the local fluid infiltration and may even have some effect on the separation of a hydrothermal phase from magma.

The results were possible because of the detailed nature of data collection, which provided information for building a detailed model of the context of the mineralization as well as allowing comprehensive cross-correlations between mineralogical and geochemical data. Methods exist today for recording and analysing large amounts of data in a full 3-dimensional interactive environment. Observations must be factual rather than subjective to the knowledge and experience of the geologist.

References

Arribas, A., Jr., Hedenquist, J.W., Itaya, T., Okada, T., Concepcion, R.A., and Garcia, J.S.J. (1995) Contemporaneous formation of adjacent porphyry and epithermal Cu-Au deposits over 3000 Ka in northern Luzon, Philippines. *Geology*, vol. 23: 337-340.

Bessinger, B. and Apps, J.A. (2003) The hydrothermal chemistry of gold, arsenic, antimony, mercury and silver. eScholarship Repository, University of California. <http://repositories.cdlib.org/lbnl/LBNL-57395>.

Boyce, Adrian. SUERRC, East Kilbride Research Park, Glasgow, Scotland

Brannon, Chuck. (Former) Chief Geologist, Grasberg pit operations. PT Freeport Indonesia.

Brimhall, G.H. and Ghiorso, M.S. (1983) Origin and ore-forming consequences of the advanced argillic alteration process in hypogene environments by magmatic gas contamination of meteoric fluids. *Economic Geology*, vol. 78: 73-90.

Brown, P.E. (1998) Fluid inclusion modelling for hydrothermal systems. *In: Richards, J.P. and Larson, P.B. (1998). Techniques in hydrothermal ore deposits geology. Reviews in economic geology*, vol. 10 Society of Economic Geology.

Burnham C.W. (1979) Magmas and hydrothermal fluids. *In: Barnes H.L. (ed.) Geochemistry of hydrothermal mineral deposits. Wiley-Interscience. New York / Chichester / Brisbane / Totonto.*

Campbell, A.R., and Larson, P.B. (1998) Introduction to stable isotope applications in hydrothermal systems. *In: Richards, J.P. and Larson, P.B. (1998). Techniques in hydrothermal ore deposits geology. Reviews in economic geology*, vol. 10 Society of Economic Geology.

Chiba, H., Kusakabe, M., Hirano, S., Matsuo, S., and Somiya, S. (1981) Oxygen isotope fractionation factors between anhydrite and water from 100 °C and 500 °C. *Earth and Planetary Science Letters*, vol53: 55-62.

Cline, J.S. and Bodnar, R.J. (1991) Can economic porphyry copper mineralisation be generated by a typical calc-alkaline melt? *Journal of Geophysical Research*, vol96: 8113-8126.

Cooke, D.R., Hollings, P., and Walshe, J.L. (2005) Giant porphyry deposits: Characteristics, distribution, and tectonic controls. *Economic Geology*, vol100: 801-818.

Coutts, Ben. Underground geologist, GBT mine. PT Freeport Indonesia.

Cox, S.F., Braun, J. and Knackstedt, M.A., (2001) Principles of structural control on permeability and fluid flow in hydrothermal systems. *Reviews in Economic Geology*, vol. 14: 1-24.

Craig, H. (1961) Isotopic variations in meteoric waters. *Science*, vol 133: 1702-1703.

Crerar and Barnes (1976)

Deer, W.A., Howie, R.A., and Zussman, J. (1992) An introduction to the rock-forming minerals. 2nd edition. Pearson Education Ltd, England.

Droop, G.T.R. (1987) A general equation for estimating Fe³⁺ concentrations in ferromagnesian silicates and oxides from microprobe analyses, using stoichiometric criteria. *Mineralogical Magazine*, vol51: 431-435.

Dube, B. and Guha, J. (1992) Relationship between northeast-trending regional faults and Archaean mesothermal gold-copper mineralisation: Cooke Mine, Abitibi Greenstone Belt, Quebec, Canada. *Economic Geology*, vol87: 1525-1540.

Einaudi, M.T., Hedenquist, J.W., and Inan, E.E. (2003) Sulphidation states of fluids in active and extinct hydrothermal systems: Transitions from porphyry to epithermal environments. In: Simmons, S.F. and Graham, I. (eds) Volcanic, geothermal, and ore-forming fluids: Rulers and witnesses of processes within the earth. Society of Economic Geologists. Special Publication 10: 285-313.

Einaudi, M.T., Meinert, L.D., and Newberry, R.J. (1981) Skarn deposits. *Economic Geology*. 75th Anniversary Volume: 317-391.

Friehauf, K.C. and Pareja, G.A. (1998) Can oxygen isotope halos be produced around high-temperature dolostone-hosted ore deposit?: Evidence from the Superior District, Arizona. *Economic Geology*, vol93: 639-650.

Gammons, C.H., and Williams-Jones, A.E. (1997) Chemical mobility of gold in the porphyry-epithermal environment. *Economic Geology*, vol92: 45-59.

Golding, Sue. University of Queensland, Brisbane, Australia

Graham, C.M., Harmon, R.S., and Sheppard, S.M.F. (1984) Experimental hydrogen isotope studies: Hydrogen isotope exchange between amphibole and water. *American Mineralogist*, vol69: 128-138.

Guha, J., Archambault, G. and Leroy J. (1983) A correlation between the evolution of mineralizing fluids and the geomechanical development of a shear zone as illustrated by the Henderson 2 Mine, Quebec. *Economic Geology*, vol. 78: 1605-1618.

Hack, A.C., and Mavrogenes, J.A. (2006) A synthetic fluid inclusion study of copper solubility in hydrothermal brines from 525 to 725°C and 0.3 to 1.7Gpa. *Geochimica et Cosmochimica Acta*, vol70: 3970-3985.

Hedenquist, J.W., Arribas, A., Jr., and Reynolds, T.J. (1998) Evolution of an intrusion-centered hydrothermal system: Far Southeast-Lepanto porphyry and epithermal Cu-Au deposits, Philippines. *Economic Geology*, vol93: 373-404.

Hedenquist J.W., and Richards, J. (1998) The influence of geochemical techniques on the development of genetic models for porphyry copper deposits. In: Richards, J.P., and Larson, P.B. (eds.). *Techniques in Hydrothermal Ore Deposits Geology. Reviews in Economic Geology*, vol. 10: 235-256.

Hefton, K.K., MacDonald, G.D., Arnold, L.C., Schappert, A.L., and Ona, A. (1995) Copper-gold deposits of the Ertsberg (Gunung Bijih) Mining District, Irian Jaya. *In: Mayes, D., and Pollard, P.J. (Eds.) Geology and copper-gold deposits of the Erstberg (Gunung Bijih) Mining District, Irian Jaya, Indonesia. 17th International Geochemical Exploration Symposium. James Cook University EGRU Contribution 53: 1-43.*

Heinrich, C.A., Gunther, D., Audetat, A., Ulrich, T., and Frischknecht, R. (1999) Metal fractionation between magmatic brine and vapor, determined by microanalysis of fluid inclusions. *Geology*, vol27, No8: 755-758.

Heinrich, C.A. (2005) The physical and chemical evolution of low-salinity magmatic fluids at the porphyry-epithermal transition: A thermodynamic study. *Mineralium Deposita*, vol39: 864-889.

Heinrich, C.A., Driesner, T., Stefansson, A. and Seward, T.M. (2004) Magmatic vapour contraction and the transport of gold from the porphyry environment to epithermal ore deposits. *Geology*, vol32: 761-764.

Heinrich, C.A., Ryan, C.G., Mernagh, T.P., and Eadington, P.J. (1992) Segregation of ore metals between magmatic brine and vapour: A fluid inclusion study using PIXE microanalysis. *Economic Geology*, vol87: 1566-1583.

Heithersay, P.S. and Walshe, J.L. (1995) Endeavour 26 North: A porphyry copper-gold deposit in late ordovician, shoshonite Goonumbla Volcanic Complex, New South Wales, Australia. *Economic Geology*, vol90: 1506-1532.

Hemley, J.J., Cygan, G.L., Fein, J.B., Robinson, G.R and d'Angelo, W.M. (1992) Hydrothermal ore-forming processes in the light of studies in rock-buffered systems: I. Iron-copper-zinc-lead sulphide solubility relations. *Economic Geology*, vol87: 1-22.

Hezerkhani, A. and Williams-Jones, A.E. (1998) Controls of alteration and mineralisation in the Sungun porphyry copper deposit, Iran: Evidence from fluid inclusions and stable isotopes. *Economic Geology*, vol93: 651-670.

Hildenbrand, T.G., Berger, B., Jachens, R.C. and Ludington, S. (2000) Regional crustal structures and their relationship to the distribution of ore deposits in the western United States, based on magnetic and gravity data. *Economic Geology*, vol95: 1583-1603.

Hill, K.C., Kendrick, R.D., Crowhurst, P.V. and Gow, P.A. (2002) Copper-gold mineralisation in New Guinea: tectonics, lineaments, thermochronology and structure. *Australian Journal of Earth Sciences*, vol49: 737-752.

Hooper, B., Heithersay, P.S., Mills, M.B., Lindhorst, J.W. and Freyberg, J. (1996) Shoshonite-hosted Endeavour 48 porphyry copper-gold deposit, Northparkes, central New South Wales. *Australian Journal of Earth Sciences*, vol43: 279-288.

Housh, T., and McMahon, T.P. (2000) Ancient isotopic characteristics of Neogene potassic magmatism in western New Guinea (Irian Jaya, Indonesia). *Lithos*, vol50: 217-239.

Hudson, D.M. (2003) Epithermal alteration and mineralisation in the Comstock District, Nevada. *Economic Geology*, vol98: 367-385.

Kesler, S.E., Chryssoulis, S.L. and Simon, G., (2002) Gold in porphyry copper deposits: its abundance and fate. *Ore Geology Reviews*, vol. 21: 103-124.

Kojima, S. and Ueno, T. (1994) A thermodynamic prediction on the stability of the nukundamite + chalcopyrite + bornite + pyrite assemblages. *Mineralogical Magazine*, vol. 58: 235-245.

Landtwing, M.R., Dillenbeck, E.D., Leake, M.H. and Heinrich, C.A. (2002) Evolution of the breccia-hosted porphyry Cu-Mo-Au deposit at Agua Rica, Argentina: Progressive unroofing of a magmatic hydrothermal system. *Economic Geology*, vol 97: 1273-1292.

Loucks, R.R., and Mavrogenes, J.A. (1999) Gold solubility in supercritical hydrothermal brines measured in synthetic fluid inclusions. *Science*, vol284: 2159-2163.

MacDonald, George. (former) Chief Geologist, Grasberg pit operations. PT Freeport Indonesia.

MacDonald, G.D., and Arnold, L.C. (1994) Geological and geochemical zoning of the Grasberg Igneous Complex, Irian Jaya, Indonesia. *Journal of geochemical exploration*, vol50: 143-178.

McDowell, F.W., McMahan, T.P., Warren, P.Q., and Cloos, M. (1996) Pliocene Cu-Au bearing intrusions of the Gunung Bijih (Ertsberg) district, Irian Jaya, Indonesia: K-Ar Geochronology. *Journal of Geology*, vol 104: 327-340.

McMahan, T.P. (1994a) Pliocene intrusions in the Gunung Bijih (Ertsberg) Mining District, Irian Jaya, Indonesia: Petrography and mineral chemistry. *International Geology Review*, vol36: 820-849.

McMahan, T.P. (1994b) Pliocene intrusions in the Gunung Bijih (Ertsberg) Mining District, Irian Jaya, Indonesia: Major- and trace-element chemistry. *International Geology Review*, vol36: 925-946.

Mancano, D.P. and Campbell, A.R. (1995) Microthermometry of enargite-hosted fluid inclusions from the Lepanto, Philippines, high-sulphidation Cu-Au deposit. *Geochemica et Cosmochimica Acta*, vol59: 3909-3916.

Manning, Peter. Data geologist, Exploration office. PT Freeport Indonesia.

Masterman, G.J., Cooke, D.R., Berry, R.F. Walshe, J.L, Lee, A.W. and Clark, A.H. (2006) Fluid chemistry, structural setting, and emplacement history of the Rosario Cu-Mo porphyry and Cu-Ag-Au epithermal veins, Collahausi District, Northern Chile. *Economic Geology*, vol 100: 835-862.

Mathur, Ryan. University of Arizona

Mathur R.D., Ruiza, J., Titley, S., Gibbins, S. and Margotomo, W. (2000) Different crustal sources for Au-rich and Au-poor ores of the Grasberg Cu–Au porphyry deposit. *Earth and Planetary Science Letters*, vol. 183: 7-14.

Mathur, R.D., Titley, S., Ruiz, J., Gibbins, S., and Frieauf, K. (2005) A Re–Os isotope study of sedimentary rocks and copper–gold ores from the Ertsberg District, West Papua, Indonesia. *Ore Geology Reviews*, vol. 26: 207-226.

Matthews, A., and Katz, A. (1977) Oxygen isotope fractionation during dolomitization of calcium carbonate. *Geochimica et Cosmochima Acta*, vol 41: 1431-1438.

Mealey, G.A. (1996) Grasberg: Mining the richest and most remote deposit of copper and gold in the world, in the mountains of Irian Jaya, Indonesia. Freeport-McMoRan Copper & Gold Inc. Tien Wah Press (Pte). Ltd., Singapore.

Meinert, L.D., Dipple, G.M., and Nicolescu, S. (2005) World skarn deposits. *Economic Geology*. 100th Anniversary Volume: 299-336.

Meinert, L.D., Hedenquist, J.W., Satoh, H., and Matsuhisa, Y. (2003) Formation of anhydrous and hydrous skarn in Cu-Au deposits by magmatic fluids. *Economic Geology*, vol98: 147-156.

Meinert, L.D., Hefton, K.K., Mayes, D., and Tasiran, I. (1997) Geology, zonation and fluid evolution of the Big Gossan Cu-Au skarn deposit, Ertsberg district, Irian Jaya. *Economic Geology*, vol 92: 509-534.

Mertig, H.J., Rubin, J.N., and Kyle, J.R. (1994) Skarn Cu-Au orebodies of the Gunung Bijih (Ertsberg) Mining District, Irian Jaya, Indonesia. *Journal of geochemical exploration*, vol50: 179-202.

Morrison, G., Kary, G., Handfield, R. and Frieda Project Staff (1999) Intrusion-related mineralisation relationships in the Frieda River Complex, Papua New Guinea. PACRIM '99, Bali, Indonesia.

Mountain, B.W., and Seward, T.M. (2003) Hydrosulphide/sulphide complexes of copper(I): Experimental confirmation of the stoichiometry and stability of $\text{Cu}(\text{HS})_2$ to elevated temperatures. *Geochimica et Cosmochimica Acta*, vol67, No16: 3005-3014.

Nash, T.J. (1976) Fluid-inclusion petrology – data from porphyry copper deposits and application to exploration. *Geological Survey Professional Paper 907-D*.

New, B.T.E., Widodo, S., Wiwoho, N., and Edwards, A. (1999) Kucing Liar, Irian Jaya: A sedimentary-hosted Cu-Au deposit. *In: Stanley, C.J. et al., (Eds.) Mineral deposits: Processes to processing. Proceedings of the 5th biennial SGA meeting and 10th quadrennial IAGOD symposium, London, vol2: 1055-1058.*

Ohmoto, H., and Rye, R.O. (1979) Isotopes of sulfur and carbon. *In Barnes, H.L. (Ed.) Geochemistry of hydrothermal ore deposits. John Wiley & Sons. 509-561.*

Oliver, N.H.S. (1996) Review and classification of structural controls on fluid flow during regional metamorphism. *Journal of Metamorphic Geology*, vol. 14: 477–492.

Ossandon, G.C., Freraut, R.C., Gustafson, L.B., Lindsay, D.D. and Zentilli, M. (2001) Geology of the Chuquicamata Mine: A progress report. *Economic Geology*, vol96: 249-270.

Padilla-Garza, R.A., Titley, S.R. and Eastoe, C.J. (2004) Hypogene evolution of the Escondida porphyry copper deposit, Chile. *Special Publication 11*. pp141-165. Society of Economic Geologists.

Parris, K. (1994a) Preliminary geological data record – Timika (3211) 1:250,000 Sheet Area, Irian Jaya: PT Freeport Indonesia Company, Exploration Division 32p. (unpublished).

Parris, K. (1994b) Central Range Irian Jaya Geology Compilation 1:500,000: PT Freeport Indonesia Company (unpublished map).

Pennington, J.B. (1995) Geology of the access road to the Ertsberg (Gunung Bijih) Mining District, Irian Jaya. *In: Mayes, D., and Pollard, P.J. (Eds.) Geology and copper-gold deposits of the Erstberg (Gunung Bijih) Mining District, Irian Jaya, Indonesia*. 17th International Geochemical Exploration Symposium. James Cook University EGRU Contribution 53: 44-63.

Peters, Lisa. New Mexico Geochronology Research Laboratory

Pollard, P.J., and Taylor, R.G. (2002) Paragenesis of the Grasberg Cu-Au deposit, Irian Jaya, Indonesia: Results from logging section13. *Mineralium Deposita*, vol37: 117-136.

Pollard, P.J., Taylor, R.G., and Peters, L. (2005) Ages of intrusion, alteration and mineralization at the Grasberg Cu-Au deposit, Papua, Indonesia. *Economic Geology*, vol100: 1005-1020.

Pollard, P.J., Taylor, R.G., and Widodo, S. (2001) Geochronology of intrusive rocks and Cu-Au mineralisation in the Ertsberg Mining District, Irian Jaya, Indonesia. *In: Williams. P.J. (Ed.) 2001: A hydrothermal odyssey. Extended Conference Abstracts. James Cook University EGRU Contribution 53: 166-167.*

Prendergast, K. (2001) Evolution of the West Grasberg breccia zone and gold-bearing limestone breccias, Ertsberg Mining District, Irian Jaya, Indonesia. *In: Williams. P.J. (Ed.) 2001: A hydrothermal odyssey. Extended Conference Abstracts. James Cook University EGRU Contribution 53: 168-169.*

Prendergast, K., Clarke, G.W., Pearson, N.J. and Harris, K. (2006) Genesis of pyrite-Au-As-Zn-Bi-Te zones associated with Cu-Au skarns: Evidence from the Big Gossan and Wanagon Gold deposits, Ertsberg District, Papua, Indonesia. *Economic Geology, vol 100: 1021-1050.*

Qin, Z., Yu, F. and Yu, J. (1987) D/H evidence for magmatic degassing of miarolitic alkaline granites in Kuiqi and Qingdao, China. *Geochemical Journal, vol21: 149-157.*

Quarles van Ufford, A. (1996) Stratigraphy, structural geology and tectonics of a young forearc-continent collision, western Central Range, Irian Jaya (western New Guinea), Indonesia. Unpublished PhD thesis, University of Texas at Austin.

Quarles van Ufford, A., and Sedgwick, P. (1998) Recession of the equatorial Puncak Jaya glaciers (~1825 to 1995), Irian Jaya (Western New Guinea), Indonesia. *Zeitschrift fur Gletscherkunde und Glazialgeologie. Band34: 131-140.*

Rice, C.M., Atkin, D., Bowles, J.F.W. and Criddle, A.J. (1979) Nukundamite, a new mineral, and idaite. *Mineralogical Magazine, vol. 43: 193-200.*

Richards, J.P. (2000) Lineament revisited. *SEG Newsletter. Number 42.*

Rowins, S.M. (2000) Reduced porphyry copper-gold deposits: A new variation on an old theme. *Geology*, vol28, No6: 491-494.

Rubin, J.N, and Kyle, J.R. (1998) The Gunung Bijih Timur (Ertsberg East) skarn complex, Irian Jaya, Indonesia: Geology and genesis of a large magnesian, Cu-Au skarn. *In: Lentz, D.R. (Ed.) Mineralised intrusion-related skarn systems. Mineralogical Association of Canada short course notes*, vol26: Chapter 8, 246-288.

Sakai, H., and Tsutsumi, M. (1978) D/H fractionation factors between serpentine and water at 100 ° to 500 °C and 2000 bar water pressure and the D/H ratios of the natural serpentines. *Earth and Planetary Science Letters*, vol40: 231-242.

Sapiies, B. and Cloos, M. (2005) Strike-slip faulting in the core of Central Range of west New Guinea: Erstberg Mining District, Indoneisa. *Geological Society of America, Bulletin*, vol116: 277-293.

Sapiie, B., Natawidjaya, D.H., and Cloos M. (1999) Strike-slip tectonics of New Guinea: Transform motion between the Caroline and Australian plates. *In: Busono, I., and Alam, H. (Eds.) Developments on Indonesian tectonics and structural geology*, vol1. *Proceedings of Indonesian Association of Geologists. 28th Annual Convention. Jakarta.*

Seedorff, E., Dilles, J.H., Proffett, J.M., Jr., Einaudi, M.T., Zurcher, L., Stavast, W.J.A., Johnson, D.A., and Barton, M.D. (2005) Porphyry deposits: Characteristics and origin of hypogene features. *Economic Geology. 100th Anniversary Volume*: 251-298.

Sheppard, T.J., Rankin, A.H., and Alderton, D.H.M. (1984). *A practical guide to fluid inclusion studies*. Blackie. Glasgow and London.

Sibson, R.H. (2001) Seismogenic framework for hydrothermal transport and ore deposition. *Reviews in Economic Geology*, vol. 14: 25-50.

Sillitoe, R.H. (1994) Erosion and collapse of volcanoes: Causes of telescoping in intrusion-centered ore deposits. *Geology*, vol22: 945-948.

Sillitoe, R.H. (1999) Styles of high-sulphidation gold, silver and copper mineralization in the porphyry and epithermal environments. In: Weber, G. (ed) Pacrim '99 Congress, Bali, Indonesia, 1999, Proceedings. AusIMM, Parkville, victoria: 29-44.

Stefansson, A., and Seward, T.M. (2004) Gold(I) complexing in aqueous sulphide solutions to 500°C and 500 bar. *Geochimica et Cosmochimica Acta*, vol68, No.20: 4121-4143.

Sunyoto, W. (2000) Geology of the Wabu skarn, Central Range, Irian Jaya, Indonesia. Unpublished MSc thesis, James Cook University.

Suzuki, T., and Epstein, S. (1976) Hydrogen isotope fractionation between OH-bearing minerals and water. *Geochimica et Cosmochimica Acta*, vol40: 1229-1240.

Taylor, H.P. (1979) Oxygen and hydrogen isotope relationships in hydrothermal mineral deposits. *In: Barnes H.L. (ed.) Geochemistry of hydrothermal mineral deposits.* Wiley-Interscience. New York / Chichester / Brisbane / Toronto.

Taylor, B.E. (1988) Degassing of rhyolite magmas: hydrogen isotope evidence and implications for magmatic-hydrothermal ore deposits. In: Taylor, R.P. and Strong, D.F. (1988) Recent advances in the geology of granite-related ore deposits. Geological Survey of Canada. Contribution 17886.

Taylor, R.G. (1992) Ore textures: recognition and interpretation. 1, Infill texture. James Cook University, EGRU.

Taylor, R.G. (1994) Ore textures: recognition and interpretation. 2, Alteration textures. James Cook University, EGRU.

Talyor, R.G. (1998) Ore textures: recognition and interpretation. 3, Overprinting. James Cook University, EGRU.

Tchalenko, J.S. (1970) Similarities between shear zones of different magnitudes. Geological Society of America Bulletin, vol. 81: 1625-1640.

Tchalenko, J.S. and Ambraseys, N.N. (1970) Structural analysis of the Dasht-e Bayaz (Iran) earthquake fractures. Geological Society of America Bulletin, vol. 81: 41-60.

Titley, Spencer. University of Arizona

Tosdal, R.M. and Richards, J.P. (2001) Magmatic and structural controls on the development of porphyry Cu ± Mo ± Au deposits. Reviews in Economic Geology, vol14:157-181.

Ulrich, T. and Heinrich, C.H. (2001a) Geology and alteration geochemistry of the porphyry Cu-Au deposit at Bajo de la Alumbrera, Argentina. Economic Geology, vol96: 1719-1742.

Ulrich, T. and Heinrich, C.H. (2001b) The evolution of a porphyry Cu-Au deposit, based on LA-ICP-MS analysis of fluid inclusions: Bajo de la Alumbrera, Argentina. Economic Geology, vol96: 1743-1774.

Vila, T. and Sillitoe, R.H. (1991) Gold-rich porphyry systems in the Maricunga Belt, northern Chile. Economic Geology, vol86: 1238-1260.

Vila, T., Sillitoe, R.H., Betzhold, J. and Viteri, E. (1991) The porphyry gold deposit at Marte, northern Chile. Economic Geology, vol86: 1271-1286.

Weiland, R.J. and Cloos, M. (1996) Pliocene-Pleistocene asymmetric unroofing of the Irian fold belt, Irian Jaya, Indonesia: Apatite fission-track thermochronology. GSA Bulletin, vol108: 1438-1449.

Widodo, S., Belluz, N., Wiwoho, N., Kusnanto, B., Manning, P., MacDonald, G.D., and Edwards, A. (1998) Geology of the Kucing Liar orebody, Irian Jaya, Indonesia. *In*: Porter, T.M. (Ed.) Porphyry and hydrothermal copper and gold deposits: A global perspective. Conference Proceedings. Australian Mineral Foundation.

Widodo, S., Manning, P., Wiwoho, Johnson, L., N., Belluz, N., Kusnanto, B., MacDonald, G.D., and Edwards, A. (1999) Progress in understanding and developing the Kucing Liar orebody, Irian Jaya, Indonesia. Pacific Rim Conference Proceedings.

Wilkins, R.W.T. (1990). The relative chronology of fluid inclusions in minerals. *In*: Herbert, H.K. and Josar, R.H. (eds.) (1990) Stable isotopes and fluid processes in mineralisation. University of Western Australia Publication No 23.

Xirochakis, D., Lindsley, D.H., and Andersen, D.J. (2001). Assemblages with titanite (CaTiSiO_4), Ca-Mg-Fe olivine and pyroxenes, Fe-Mg-Ti oxides, and quartz: Part I. Theory. *American Mineralogist*, vol. 86: 247-253.

Zheng, Y.F. (1993) Calculation of oxygen isotope fractionation in anhydrous silicate minerals. *Geochimica et Cosmochimica Acta*, vol57: 1079-1091.

Appendix I: Drillhole positioning and survey

PATTERNS OF DRILLING AT KUCING LIAR

All data collected for this research is derived from a pattern of diamond drilling intended to measure the Kucing Liar resource. The drilling is conducted from a single elevation from a level expressly excavated for purpose of exploration. Excavations spaced at 50m intervals along this drive were completed for drilling stations, of which 16 were originally completed spaced 100m apart covering 1,500 metres of regional stratigraphic strike (Chapter 1). Only these drill holes are included in this research program. Later infill drilling was conducted in the centre of deposit to confirm continuity of the resource at a distance of 50m. The data collected from these holes was found to correlate well with the data collected on 100m spacing. Drilling was conducted along an azimuth of 39-219°, which is perpendicular to the regional strike of stratigraphy. The drill stations are labelled with the prefix KL, followed by the station number and a number exclusive to each hole (eg. KL16-03, KL32-04). The dip and azimuth of each drill hole have been surveyed every 3m on average and this data has been used to position each sample interval. The layout of all holes drilled from each station is illustrated in Chapter 1. Collar positions and orientation at start of hole for all drilling is recorded in Table I-1. A file of downhole survey data is provided in digital format.

TABLES OF DRILL HOLE LOCATIONS AND DIRECTIONS

The northing, easting and elevation of the collar location of each drillhole examined for the research program plus the total depth of the drillhole and the planned azimuth and dip of each are included in the following table. The downhole survey information including dip and dip direction were measured at regular 3m intervals for each hole and the records are presented in the digital file *drillholes.xls* along with all collar information.

Table I-1 Drill hole locations and orientations at collar

Hole	Northing(m)	Easting(m)	Elevation(m)	Depth(m)	Azimuth(°)	Dip(°)
KL16-01	9549813.741	734889.575	3028.321	489.0	219.98	-86.75
KL16-02	9549813.760	734889.375	3028.431	180.0	220.07	-71.26
KL16-03	9549814.009	734889.004	3028.781	191.5	219.76	-41.14
KL16-04	9549813.381	734889.537	3031.321	191.2	219.18	33.60
KL16-05	9549814.001	734889.625	3032.851	218.2	219.21	51.58
KL16-06	9549817.646	734893.129	3028.301	1051.2	38.94	-86.51
KL16-07	9549814.275	734892.804	3028.251	678.4	38.83	-76.94
KL16-08	9549817.006	734893.361	3028.371	380.3	49.83	-67.16
KL16-09	9549817.147	734893.800	3028.091	614.6	45.12	-46.36
KL18-01	9549959.832	734843.019	3032.681	330.5	161.66	-84.32
KL18-02	9549962.490	734841.636	3031.191	323.5	218.15	-65.79
KL18-03	9549960.109	734841.878	3030.421	235.0	217.26	-36.27
KL18-04	9549959.910	734841.900	3030.991	216.2	212.88	-19.72
KL18-05	9549959.791	734841.849	3031.461	227.0	212.32	2.60
KL18-06	9549961.259	734840.956	3034.041	326.3	215.55	34.11
KL18-07	9549967.538	734847.728	3030.101	407.0	35.81	-75.89
KL18-08	9549966.721	734848.099	3030.101	525.7	35.78	-59.41
KL18-09	9549961.662	734843.067	3035.091	431.2	217.70	49.47
KL18-10	9549966.696	734846.009	3030.211	885.0	42.76	-48.18
KL20-01	9550107.647	734806.450	3031.711	416.6	220.93	-83.24
KL20-02	9550107.518	734806.480	3031.611	377.5	220.84	-71.05
KL20-03	9550107.239	734806.230	3033.651	538.0	220.30	-54.65
KL20-04	9550106.816	734805.812	3031.711	501.7	219.87	-40.06
KL20-05	9550106.488	734805.552	3032.121	433.5	219.01	-27.94
KL20-06	9550106.716	734805.772	3033.011	409.5	218.85	-8.25
KL20-07	9550110.971	734809.166	3031.651	389.4	36.49	-82.65
KL20-08	9550110.971	734809.166	3031.651	468.3	36.49	-82.65
KL20-09	9550111.482	734809.484	3032.011	645.2	36.33	-63.64
KL22-01	9550228.113	734796.102	3033.541	511.0	37.92	-84.00
KL22-02	9550228.263	734796.141	3032.051	549.0	36.74	-75.68
KL22-03	9550224.087	734792.348	3032.071	505.0	221.49	-85.04
KL22-04	9550223.946	734792.147	3032.101	600.0	219.18	-75.23
KL22-05	9550223.997	734792.138	3032.151	871.6	220.26	-60.09
KL22-06	9550223.256	734791.599	3032.781	584.9	220.76	-45.54
KL22-07	9550222.415	734790.820	3032.481	436.3	221.49	-28.77
KL22-08	9550222.025	734790.641	3032.701	360.1	220.10	-14.45
KL22-09	9550222.105	734790.551	3035.931	419.2	220.01	1.42
KL22-10	9550222.003	734789.621	3035.611	295.0	37.92	-59.00
KL24-01	9550229.701	734646.200	3047.111	506.8	220.96	-84.53
KL24-02	9550229.142	734646.560	3047.411	460.0	219.09	-69.17
KL24-03	9550229.103	734646.461	3047.431	904.0	219.57	-58.09
KL24-04	9550231.397	734644.007	3048.201	914.7	267.52	-19.13
KL24-05	9550229.869	734646.103	3047.261	373.0	220.84	-40.58
KL24-06	9550229.441	734645.610	3048.071	374.5	220.29	-18.00
KL24-07	9550229.091	734645.591	3048.231	349.6	222.84	-2.59
KL24-08	9550229.080	734645.742	3048.961	388.0	221.76	13.74
KL24-09	9550229.070	734645.881	3050.151	577.7	216.96	27.20
KL24-10	9550233.678	734648.263	3046.897	684.0	45.79	-76.15
KL24-11	9550233.787	734648.504	3046.898	651.5	44.80	-59.63

Table I-1 Drill hole locations and orientations at collar (cont.)

Hole	Northing(m)	Easting(m)	Elevation(m)	Depth(m)	Azimuth(°)	Dip(°)
KL26-01	9550269.782	734550.989	3049.071	498.3	218.54	-46.45
KL26-02	9550270.112	734551.433	3049.502	993.0	218.46	-62.77
KL26-03	9550270.551	734551.328	3048.931	775.1	218.45	-80.01
KL26-04	9550269.910	734550.761	3049.241	485.4	218.37	-35.00
KL26-05	9550269.939	734550.829	3050.371	436.6	217.21	1.99
KL26-06	9550273.284	734553.405	3049.121	364.2	38.37	-80.10
KL26-07	9550273.240	734553.365	3049.504	205.0	39.62	-81.18
KL26-08	9550272.695	734553.177	3048.745	689.8	39.44	-81.43
KL26-09	9550269.914	734550.665	3050.787	418.1	219.43	-19.00
KL26-10	9550269.989	734550.723	3050.903	450.0	219.21	12.59
KL26-11	9550487.452	734723.680	3036.141	451.2	198.96	-84.72
KL28-01	9550312.035	734455.568	3052.921	824.9	217.68	-42.90
KL28-02	9550312.010	734455.517	3053.751	658.4	218.02	-28.00
KL28-03	9550312.071	734455.558	3053.491	433.0	217.65	-9.11
KL28-04	9550312.280	734455.757	3052.391	855.0	216.18	-59.18
KL28-05	9550311.892	734455.664	3052.226	843.0	219.76	-75.20
KL28-06	9550323.336	734462.120	3052.880	636.0	38.42	-83.00
KL28-07	9550316.301	734458.906	3052.012	738.0	38.79	-70.10
KL28-08	9550318.642	734460.509	3054.545	1024.0	37.79	-59.40
KL28-09	9550567.512	734703.391	3037.011	501.2	221.91	-86.03
KL30-01	9550353.585	734359.660	3053.975	840.0	221.21	-44.04
KL30-02	9550353.429	734359.946	3054.291	459.3	217.65	-27.01
KL30-03	9550353.288	734359.837	3054.171	486.9	217.29	-13.00
KL30-04	9550353.609	734360.137	3055.161	439.0	217.21	2.75
KL30-05	9550353.940	734360.946	3053.921	768.0	217.43	-70.80
KL30-06	9550353.976	734361.035	3053.861	798.0	219.02	-84.05
KL30-07	9550353.454	734360.490	3055.440	419.5	217.85	17.60
KL30-08	9550357.930	734363.250	3053.444	926.8	40.49	-74.15
KL30-09	9550761.610	734658.073	3038.385	557.5	220.68	-61.26
KL32-01	9550397.896	734263.800	3056.281	315.8	219.52	0.97
KL32-02	9550396.083	734268.552	3057.171	416.0	219.32	-22.22
KL32-03	9550396.079	734268.551	3056.252	601.0	219.01	-37.30
KL32-04	9550396.214	734268.647	3056.133	693.0	219.62	-63.24
KL32-05	9550396.560	734268.873	3056.061	775.7	220.29	-75.00
KL32-06	9550395.990	734268.415	3058.465	438.0	218.85	17.75
KL32-07	9550399.112	734270.984	3056.132	819.0	38.67	-87.71
KL32-08	9550402.130	734271.902	3056.220	992.8	40.42	-60.41
KL32-09	9550403.469	734272.845	3056.034	611.5	37.42	-28.11
KL32-10	9550396.510	734268.068	3060.214	518.5	216.95	40.07
KL32-11	9550401.303	734271.546	3052.740	476.7	36.17	-71.77
KL34-01	9550436.237	734172.427	3059.652	567.7	218.24	-0.33
KL34-02	9550436.351	734172.575	3056.298	733.7	217.26	-43.97
KL34-03	9550436.837	734172.819	3058.163	734.7	218.84	-75.00
KL34-04	9550437.051	734172.845	3058.207	734.7	218.35	-88.83
KL34-05	9550436.526	734172.651	3058.145	809.5	218.90	-64.27
KL34-06	9550436.300	734172.573	3058.585	665.8	217.40	-31.70
KL34-07	9550436.254	734172.423	3059.138	518.7	217.04	-15.33
KL34-08	9550440.912	734176.740	3058.037	526.2	38.01	-74.40
KL34-09	9550441.669	734177.340	3058.071	1229.4	42.40	-45.73
KL34-10	9550449.590	734190.851	3057.972	425.7	39.42	-60.63

Table I-1 Drill hole locations and orientations at collar (cont.)

Hole	Northing(m)	Easting(m)	Elevation(m)	Depth(m)	Azimuth(°)	Dip(°)
KL36-01	9550481.311	734077.303	3062.268	371.4	218.29	0.28
KL36-02	9550481.614	734077.516	3060.802	473.5	218.13	-45.06
KL36-03	9550481.854	734077.868	3060.538	762.8	218.79	-63.88
KL36-04	9550481.578	734077.664	3064.063	563.0	216.70	30.02
KL36-05	9550482.144	734078.029	3060.724	781.5	217.85	-87.89
KL36-06	9550485.406	734081.243	3060.486	1045.5	37.94	-59.64
KL36-07	9550486.832	734082.349	3057.296	474.6	38.31	-29.88
KL36-08	9550485.546	734081.040	3060.396	400.0	31.18	-75.21
KL38-01	9550525.144	733978.280	3064.627	621.4	275.11	2.02
KL38-02	9550521.528	733977.557	3064.611	242.8	218.38	0.26
KL38-03	9550521.960	733978.102	3063.688	456.5	217.79	-44.04
KL38-04	9550521.960	733978.102	3063.688	488.5	217.79	-44.04
KL38-05	9550522.616	733978.537	3063.453	1031.7	220.02	-61.03
KL38-06	9550522.484	733978.354	3063.180	497.3	218.76	-87.40
KL38-07	9550527.017	733982.569	3060.518	312.0	31.94	-75.13
KL38-08	9550527.017	733982.569	3060.518	599.0	31.94	-75.13
KL40-01	9550561.244	733889.032	3065.113	230.5	217.99	-14.50
KL40-02	9550561.770	733889.444	3064.489	594.4	217.02	-45.13
KL40-03	9550562.286	733889.762	3064.313	932.5	223.05	-74.07
KL40-04	9550567.038	733892.881	3064.020	809.1	37.76	-60.88
KL40-05	9550567.969	733893.569	3064.021	677.7	37.13	-29.90
KL40-06	9550566.640	733892.513	3064.045	808.6	31.67	-86.40
KL40-07	9550561.867	733885.429	3064.158	909.6	217.66	-60.69
KL40-08	9550561.405	733885.043	3064.624	495.0	218.59	-32.94
KL40-09	9550566.542	733888.755	3064.064	782.7	36.99	-74.65
KL42-01	9550601.985	733794.661	3068.424	343.5	219.12	-1.88
KL42-02	9550602.071	733794.761	3068.385	830.5	218.51	-59.68
KL42-03	9550602.863	733795.434	3067.798	1139.5	216.82	-86.40
KL42-04	9550602.038	733794.706	3066.566	365.7	219.10	-28.45
KL42-05	9550607.214	733798.695	3068.799	629.0	41.69	-76.50
KL42-06	9550608.212	733799.492	3067.069	774.3	38.24	-45.27
KL42-07	9550603.471	733795.006	3067.493	590.6	220.37	-45.67
KL42-08	9550603.186	733795.897	3069.831	407.6	218.52	35.76
KL42-09	9550607.351	733798.837	3066.883	820.6	37.90	-60.25
KL42-10	9550608.592	733799.823	3066.898	713.3	37.53	-30.01
KL44-01	9550641.470	733696.921	3069.323	208.0	220.94	-14.99
KL44-02	9550641.883	733697.256	3068.712	866.9	221.12	-44.70
KL44-03	9550642.366	733697.601	3068.842	956.8	223.63	-74.64
KL44-04	9550649.744	733703.680	3067.937	955.6	38.17	-60.10
KL44-05	9550651.092	733704.969	3067.880	778.6	42.58	-29.39
KL44-06	9550649.419	733703.417	3068.055	842.5	40.56	-85.83
KL44-07	9550642.850	733697.607	3068.338	638.4	222.32	-56.82
KL44-08	9550641.875	733697.170	3067.921	556.6	221.40	-30.16
KL44-09	9550642.595	733698.057	3069.194	935.5	216.86	-84.79
KL44-10	9550647.286	733701.953	3068.120	824.0	40.22	-74.35
KL46-01	9550686.196	733606.192	3069.878	951.0	219.68	-85.71
KL46-02	9550685.310	733605.495	3070.160	665.5	219.24	-59.10
KL46-03	9550685.308	733605.442	3069.909	565.8	218.10	-30.71
KL46-04	9550692.455	733611.051	3069.788	954.5	38.76	-74.75
KL46-05	9550693.162	733611.613	3069.791	827.1	37.10	-44.88

Appendix II – Thin section staining procedure

STAINING PROCEDURE

- A thin section was prepared of each rock sample without a cover slip.
- Two solutions were prepared:
 - Solution A: Alizarin Red S, concentration of 0.2g/100mL of 1.5% HCl
 - Solution B: Potassium ferricyanide, concentration of 2g/100mL 1.5% HCl
- The solutions A and B were mixed in the proportions of 3 parts by volume of A to 2 parts of B.
- One half of each thin section was immersed in the mixture of solutions for 30-45 seconds, gently agitated for part of the time to remove gas bubbles from the surface.
- Each thin section was then washed in running water for a few seconds and allowed to dry.
- A cover slip was placed over each thin section.

Appendix III – SEM analysis

RESULTS AND STOICHIOMETRIC CALCULATION

Total iron was determined as Fe²⁺ and Fe³⁺ has been calculated using the methods of Deer *et al.*, (1969) and Droop (1987) to determine the andradite component. The formula used is:

$$F = 2X.(1-T/S)$$

Where F is the number of Fe³⁺ ions per X number of oxygen ions, T is the ideal number of cations per unit formula and S is the cation total obtained when all iron is assumed to be Fe²⁺.

A problem was encountered in some garnets with very high Fe³⁺ values producing negative grossular norms. Analyses of green garnet from sample KL26-8 385.4m gave high negative values of almandine, which have low total Fe analyses (~4%) and low totals. Calculation of analyses of red garnet (matrix alteration) from the same sample did not give any problems. In the case of negative grossular norms, it is clearly established that all of the iron present is trivalent and so the grossular content was assigned to zero and the remaining compositions were renormalised without grossular. In the case of negative almandine calculations, the garnet composition was calculated assuming all iron is present in divalent form, negating the recalculation of Fe³⁺. However it was found that these compositions calculated for the green garnets in sample KL26-8 385.4m do not have correct totals of trivalent and divalent ions and so are not presented with other data.

Appendix IV – Mineral abundances logging

DRILLING DATABASE

Estimation of mineral abundances

Abundances of each recognisable mineral phase have been estimated from hand samples representative of all assay intervals from the Kucing Liar drilling. In many cases, the estimation is of a single mineral, but in some instances, it is the abundance of an assemblage of minerals. Problems were encountered in maintaining consistent identification of humite, serpentine, clay and calcite. Each of these is likely to be underestimated in the log sheets. In addition, the representation of quartz veins is not believed to be precise as they are discrete and widely spaced and as such inclusion in the skeleton core samples is not as reliable as for minerals. As the large majority of interval lengths are a single length (Figure IV-1), the estimated percentages are assumed to have equal weight for calculations. As the drill core is not oriented no structural information such as fracture or slickensides orientations have been recorded.

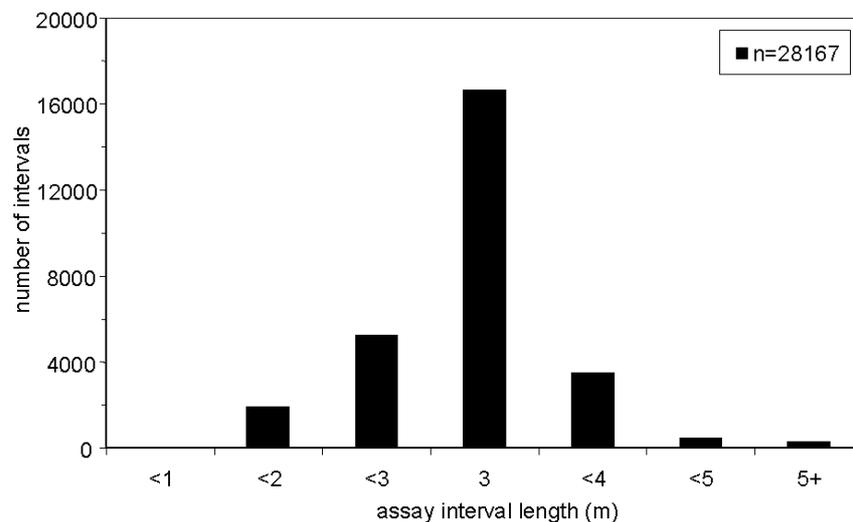


Figure IV-1 Assay interval lengths

All estimations of mineral abundances were confined to the assay interval length to provide direct comparisons.

Database fields

A digital file of the Kucing Liar drillhole logs that includes estimated mineral abundances for each sample interval of every drillhole in the Kucing Liar delineation program is included on compact disc (CD) media.

Table V-1 Fields and descriptions present in drilling database

Hole	Drill hole identifier
From	Top depth of drill interval
To	Bottom depth of drill interval
Unit	Lithological unit name
Lith	Original rock type (dolomite, limestone, sandstone, shale, porphyry)
cc-mg	Percentage marble + calcite alteration + spotty magnetite
Pyx	Percentage pyroxene alteration/infill
Gnt	Percentage garnet alteration/infill
Hmfo	Percentage humite alteration/infill
Phl	Percentage phlogopite alteration/infill
Kfs	Percentage K-feldspar alteration/infill
Bio	Percentage biotite alteration/infill
Qvn	Quartz vein intensity (1-5)
Mnt	Percentage magnetite alteration/infill
Amp	Percentage amphibole alteration/infill
Anh	Percentage anhydrite alteration/infill
qtz	Percentage silica alteration/infill
Clay	Percentage clay (unidentifiable) + talc + muscovite
Fnpy	Percentage fine pyrite alteration/infill
Cspy	Percentage coarse pyrite alteration/infill
Pyrh	Percentage pyrrhotite alteration/infill
Cpy	Percentage chalcopyrite alteration/infill
Cov	Percentage covellite alteration/infill
Moly	Percentage molybdenum alteration/infill
Glsp	Percentage galena-sphalerite alteration/infill
Hem	Percentage haematite alteration/infill
Ser	Percentage serpentine alteration/infill

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL16-01	0	3	0.84	8400	0.62	5.6	104	45	34	500	0.01	12	1.6	2.8	24	0.01
KL16-01	3	6.5	0.51	5100	0.56	0.6	115	42	12	216	0.01	10	3	6.2	27	0.01
KL16-01	6.5	9	1.92	19200	2.11	2.7	188	32	17	254	0.01	14	0.3	23.3	26	0.01
KL16-01	9	12	0.825	8250	1.42	0.7	65	14	11	62	1	10	0.01	8.8	18	0.01
KL16-01	12	15	0.83	8300	0.97	0.9	47	18	87	51	0.01	12	7.2	9.0	23	0.01
KL16-01	15	18	0.48	4800	0.48	0.8	190	45	47	1190	0.01	15	1	11.0	29	0.01
KL16-01	18	23.4	0.6	6000	0.51	1.1	162	63	25	810	0.01	11	1	10.4	51	0.01
KL16-01	23.4	26	0.43	4300	0.68	1.1	239	86	23	360	0.01	11	0.5	6.1	46	0.01
KL16-01	26	28.3	0.4	4000	0.41	0.9	290	179	13	950	0.01	6	0.4	8.0	21	0.01
KL16-01	28.3	31.5	0.49	4900	0.7	0.8	167	34	12	1460	0.01	9	0.2	7.2	29	0.01
KL16-01	31.5	33	0.95	9500	0.84	1.2	299	27	21	40	2	16	0.4	29.5	35	0.01
KL16-01	33	36	0.81	8100	0.94	1.5	7200	52	15	41	4	26	0.5	21.6	20	0.01
KL16-01	36	39	0.54	5400	1.08	2.7	4320	97	15	6	8	29	0.9	33.8	23	0.01
KL16-01	39	42	1.43	14300	1.42	2.7	6000	68	19	4	1	24	0.8	65.0	35	0.01
KL16-01	42	45	0.47	4700	1.9	2.1	4300	53	12	7	1	12	0.4	36.4	26	0.01
KL16-01	45	48	0.36	3600	0.42	1.5	12300	70	11	3	1	28	0.6	38.0	25	0.01
KL16-01	48	51	0.81	8100	0.79	2.1	6800	45	15	6	0.01	30	0.4	18.2	17	0.01
KL16-01	51	54	0.34	3400	1.2	1.9	13800	29	17	29	0.01	15	0.3	45.0	21	0.01
KL16-01	54	55.6	0.35	3500	0.93	1.6	4050	54	9	5	2	31	0.6	48.0	28	0.01
KL16-01	55.6	57.7	0.3	3000	1.17	1.8	33100	55	12	6	1	39	0.4	12.6	32	0.01
KL16-01	57.7	60.6	0.105	1050	0.13	0.01	680	16	1	29	0.01	11	0.3	9.6	17	0.01
KL16-01	60.6	61.7	1.21	12100	0.78	1.9	630	25	2	125	0.01	38	0.2	43.2	38	0.01
KL16-01	61.7	65	0.52	5200	0.49	1	510	24	0.01	260	0.01	30	0.5	15.4	29	0.01
KL16-01	65	67.7	2.97	29700	1.47	4.1	470	34	4	320	1	56	0.5	15.0	58	0.01
KL16-01	67.7	70.8	4.05	40500	1.63	6.5	11400	760	5	850	12	44	0.4	12.0	76	0.01
KL16-01	70.8	73.3	0.54	5400	0.51	2.1	223	101	3	740	1	18	0.3	5.0	61	0.01
KL16-01	73.3	76	1.23	12300	0.44	2.6	36	27	4	250	0.01	14	0.2	4.0	74	0.01
KL16-01	76	79	1.5	15000	0.86	6	95	47	20	1030	2	16	0.2	8.0	78	0.17
KL16-01	79	81	1.26	12600	1.3	3.3	65	37	5	200	1	15	1	5.0	118	0.01
KL16-01	81	84	1.55	15500	2.24	2.2	83	15	2	108	5	15	0.4	8.0	104	0.01
KL16-01	84	87	1.26	12600	0.52	4.3	25	13	3	30	1	10	0.01	8.5	117	0.01
KL16-01	87	90	1.19	11900	1.9	3	26	26	3	30	1	13	0.4	4.0	98	0.01
KL16-01	90	93	2.18	21800	2.73	4.2	91	20	13	34	1	15	0.5	5.0	115	0.11
KL16-01	93	96	1.43	14300	0.46	2.3	62	54	9	74	2	11	0.3	16.0	128	0.01
KL16-01	96	99	1.44	14400	0.36	2.7	44	69	35	39	1	10	1.4	4.5	115	0.01
KL16-01	99	102	1.81	18100	0.39	3	36	45	5	62	2	10	0.3	9.0	138	0.11
KL16-01	102	105	1.11	11100	0.43	2.4	24	11	13	91	1	10	0.5	10.0	115	0.01
KL16-01	105	108	1.13	11300	0.61	2.1	32	17	19	97	1	16	0.8	9.3	73	0.01
KL16-01	108	111	1.15	11500	0.59	2.6	50	12	14	133	2	13	0.4	17.8	65	0.01
KL16-01	111	114	1.47	14700	0.64	3.1	41	10	25	224	2	14	0.5	13.0	54	0.01
KL16-01	114	117	2.1	21000	0.73	3.1	32	10	95	145	3	14	1.2	18.0	53	0.01
KL16-01	117	120	2.28	22800	1.53	4.9	110	15	85	590	2	11	0.6	20.0	46	0.01
KL16-01	120	123	2.2	22000	3.43	3.6	56	18	73	930	1	18	0.9	26.0	70	0.1
KL16-01	123	126	1.58	15800	0.9	2.4	52	18	59	135	3	16	0.6	10.0	54	0.01
KL16-01	126	129	1.66	16600	0.57	2.5	57	30	100	273	4	11	0.8	12.0	52	0.01
KL16-01	129	132	3.78	37800	2.94	7.2	65	38	280	363	6	15	1.5	19.0	62	0.01
KL16-01	132	135	8.2	82000	5.62	13.8	36	17	300	190	3	8	0.8	34.0	50	0.14
KL16-01	135	138	3.56	35600	3.83	7.8	78	52	78	207	70	16	0.3	18.5	80	0.01
KL16-01	138	141	5.01	50100	4.82	11.5	197	50	74	177	7	21	0.4	11.0	78	0.01
KL16-01	141	144	11.6	116000	13	19.5	167	30	150	108	49	14	1.7	12.5	85	0.01
KL16-01	144	147	5.92	59200	5.14	8.3	149	18	130	189	580	31	1.6	24.0	102	0.1
KL16-01	147	148.7	13.4	134000	4.84	26.4	257	34	130	28	2	16	1.7	30.0	80	0.1
KL16-01	148.7	150.6	11.8	118000	4.76	4.3	265	15	220	19	4	64	1.5	90.0	62	0.01
KL16-01	150.6	152.7	6.01	60100	2.26	7	113	10	180	20	2	24	2	56.0	80	0.01
KL16-01	152.7	155.7	16.1	161000	20.8	1.6	341	14	25	88	8	76	0.01	45.0	51	0.01
KL16-01	155.7	157.2	2.87	28700	1.82	0.8	98	20	16	107	2	17	0.01	11.0	86	0.01
KL16-01	157.2	159	1.1	11000	2.95	0.6	205	25	15	16	5	42	0.2	8.5	32	0.01
KL16-01	159	161.8	1.39	13900	1.29	0.6	162	27	4	19	1	38	0.7	12.0	40	0.01
KL16-01	161.8	163.7	2.11	21100	1.02	1.3	57	24	12	44	1	28	0.5	7.0	70	0.01
KL16-01	163.7	166	11.7	117000	3.93	5.2	312	32	45	86	2	88	1.7	55.0	63	0.01
KL16-01	166	168	2.92	29200	2.47	1.7	120	24	4	33	2	45	0.01	9.0	34	0.01
KL16-01	168	169	0.95	9500	0.63	0.01	80	31	5	45	1	43	1.6	4.0	45	0.01
KL16-01	169	172.8	10.4	104000	2.61	19.1	4250	100	55	127	87	160	0.5	62.5	65	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL16-01	172.8	175.2	2.8	28000	4.67	16.2	11900	127	22	42	123	161	0.4	36.0	107	0.01
KL16-01	175.2	177	1	10000	7.08	6.4	3300	78	6	9	380	67	0.01	13.5	55	0.01
KL16-01	177	180	1.01	10100	4.8	10.3	4000	13	1	8	16	64	0.01	9.5	30	0.01
KL16-01	180	183	3.17	31700	3.4	6.8	840	27	29	20	4	227	0.9	29.0	38	0.01
KL16-01	183	186	1.29	12900	1.8	2.7	420	21	22	190	10	123	1	20.5	57	0.01
KL16-01	186	189	0.54	5400	4.52	3.1	1410	17	21	8	41	46	0.01	4.8	60	0.01
KL16-01	189	192	0.67	6700	0.77	3.2	540	15	7	4	11	90	0.3	9.2	54	0.01
KL16-01	192	195	1.06	10600	2.04	3.6	1000	24	3	52	4	49	0.01	7.5	50	0.01
KL16-01	195	198	1.39	13900	3.22	6.4	4100	25	3	19	4	55	0.01	5.0	27	0.01
KL16-01	198	201	0.62	6200	1.56	2.4	1680	29	11	22	5	81	0.01	12.4	30	0.01
KL16-01	201	204	3.16	31600	4.14	6	3000	96	12	470	6	65	2.1	19.0	39	0.01
KL16-01	204	207	4.56	45600	4.56	7.3	490	35	11	228	2	100	0.3	16.0	58	0.01
KL16-01	207	210	5.98	59800	3.79	9.1	1030	1520	7	43	0.01	92	0.01	11.0	30	0.01
KL16-01	210	212	4	40000	4.76	4.2	201	14	110	430	0.01	51	0.5	4.0	39	0.01
KL16-01	212	213.5	1.11	11100	1.31	1	114	10	24	19	0.01	25	0.2	6.0	48	0.01
KL16-01	213.5	215.5	0.49	4900	0.7	0.8	76	13	46	18	0.01	16	0.01	4.8	47	0.01
KL16-01	215.5	217.1	0.61	6100	0.67	1	102	14	28	19	0.01	13	0.01	2.0	30	0.01
KL16-01	217.1	219	3.1	31000	3.56	4.7	284	15	8	47	1	68	0.01	10.5	54	0.01
KL16-01	219	222	1.97	19700	2.08	3.6	164	11	27	36	0.01	41	0.3	12.5	58	0.01
KL16-01	222	225	2.57	25700	4.66	10.5	384	10	4	56	2	76	0.01	8.0	60	0.01
KL16-01	225	228	1.2	12000	1.16	2.6	140	9	0.01	86	0.01	42	0.01	5.5	40	0.01
KL16-01	228	230.7	2.63	26300	3.71	4.3	260	11	2	37	0.01	50	0.01	8.0	38	0.01
KL16-01	230.7	233.7	5.92	59200	3.89	9.3	286	16	1	160	0.01	79	0.2	11.0	46	0.01
KL16-01	233.7	236	4.2	42000	4.98	8	2700	22	5	160	0.01	121	0.01	14.5	47	0.01
KL16-01	236	239	1.62	16200	1.88	2.5	321	20	7	151	0.01	43	0.2	9.0	53	0.01
KL16-01	239	242	1.4	14000	2.43	2.9	141	34	5	129	0.01	37	0.6	7.0	106	0.01
KL16-01	242	245	3.87	38700	3.68	5.4	348	31	19	216	0.01	69	0.5	6.0	62	0.01
KL16-01	245	246.8	1.84	18400	2.94	3.2	156	65	9	80	0.01	56	1.6	9.0	50	0.01
KL16-01	246.8	249	1.6	16000	1.57	5.8	282	160	25	236	0.01	53	0.9	15.0	47	0.01
KL16-01	249	252	1.95	19500	1.87	8.2	740	279	34	920	1	84	1.4	27.0	52	0.01
KL16-01	252	255	0.88	8800	1.49	4.2	309	100	29	33	0.01	34	0.7	48.5	46	0.01
KL16-01	255	258	1	10000	1.28	3.4	202	119	28	39	2	38	0.4	59.0	65	0.01
KL16-01	258	261.1	0.75	7500	0.83	2.8	142	70	76	82	1	35	0.4	27.4	45	0.01
KL16-01	261.1	264	0.73	7300	2.63	3.2	369	146	120	15	3	21	0.7	10.4	36	0.01
KL16-01	264	267	0.5	5000	3.59	2.5	327	147	68	6	6	18	0.7	8.4	36	0.01
KL16-01	267	270	1.42	14200	3.79	4.3	63	64	110	19	1	26	0.5	9.5	46	0.01
KL16-01	270	271.7	1.11	11100	2.55	3.3	52	50	63	38	1	61	0.6	33.5	50	0.01
KL16-01	271.7	274.7	0.68	6800	1.07	2.5	102	20	4	27	0.01	94	0.4	7.2	32	0.01
KL16-01	274.7	279	1	10000	0.68	2	99	10	2	18	0.01	58	0.2	4.5	20	0.01
KL16-01	279	281.9	0.82	8200	0.72	2.2	213	68	5	11	0.01	32	0.5	5.4	45	0.01
KL16-01	281.9	285	0.56	5600	1.32	1.3	97	40	180	6	1	33	0.7	11.8	50	0.01
KL16-01	285	288	0.94	9400	1.3	2.6	37	21	110	20	0.01	23	0.5	6.5	50	0.01
KL16-01	288	291	3.66	36600	4.5	11.3	172	60	50	49	0.01	55	0.4	16.0	57	0.01
KL16-01	291	293.8	0.88	8800	2.08	3.4	127	70	140	63	1	42	0.3	13.0	56	0.01
KL16-01	293.8	296.8	0.73	7300	1.52	2.1	107	100	130	21	2	32	0.6	4.8	66	0.01
KL16-01	296.8	298.6	1.95	19500	2.36	5.1	123	56	43	14	2	54	0.6	29.0	76	0.01
KL16-01	298.6	301.7	0.35	3500	1.14	1.3	66	65	160	21	2	21	0.4	32.0	89	0.01
KL16-01	301.7	304.3	0.33	3300	1.61	0.9	36	34	330	28	1	18	0.6	6.5	71	0.01
KL16-01	304.3	305.4	5.12	51200	7.04	14.7	154	57	23	19	2	73	0.9	21.0	85	0.01
KL16-01	305.4	307.5	0.86	8600	1.69	2.7	54	40	140	117	2	26	0.5	22.8	104	0.01
KL16-01	307.5	310	2.62	26200	2.83	7	6500	68	31	31	4	32	0.7	26.0	98	0.01
KL16-01	310	314.2	5.5	55000	4.92	9.4	620	108	18	73	15	27	1.4	24.0	75	0.01
KL16-01	314.2	317.3	1.17	11700	1.41	3.1	243	37	16	46	6	16	0.5	37.0	78	0.01
KL16-01	317.3	320.6	0.65	6500	1.35	3.1	450	29	22	2	70	7	0.5	67.0	69	0.01
KL16-01	320.6	323.7	0.35	3500	1	1.5	135	15	32	8	8	9	0.01	27.0	45	0.01
KL16-01	323.7	326.5	0.97	9700	1.24	2.9	194	12	28	25	3	9	0.01	21.0	55	0.01
KL16-01	326.5	330	1.32	13200	1.04	2.8	320	21	35	48	0.01	10	0.2	19.0	86	0.01
KL16-01	330	333	1.71	17100	1.25	3.2	3480	24	22	97	0.01	10	0.01	15.5	73	0.01
KL16-01	333	335.4	1.66	16600	1.63	3.2	12700	25	18	75	4	21	0.7	28.0	40	0.01
KL16-01	335.4	337.5	0.63	6300	4.75	1.4	800	20	89	22	2	7	0.4	7.4	67	0.01
KL16-01	337.5	340	0.195	1950	0.68	0.01	336	18	40	48	0.01	7	0.01	5.3	58	0.01
KL16-01	340	343	0.24	2400	2.07	0.01	55	18	29	168	0.01	8	0.3	6.0	68	0.01
KL16-01	343	345	0.146	1460	2.43	0.01	60	45	29	40	1	11	0.6	7.8	70	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL16-01	345	348	0.82	8200	2.05	2.9	72	30	39	372	2	81	0.9	13.8	73	0.01
KL16-01	348	351	2.06	20600	2.28	8.5	160	20	26	138	2	94	1.2	20.0	61	0.01
KL16-01	351	354	0.82	8200	1.68	5.6	4700	1700	76	48	0.01	60	2.8	3.9	82	0.01
KL16-01	354	357	0.5	5000	4.32	6.1	27800	870	170	3	0.01	32	1.5	3.3	84	0.01
KL16-01	357	360	0.2	2000	0.95	1.8	3400	64	40	14	0.01	6	0.01	4.3	75	0.01
KL16-01	360	363	0.67	6700	1.15	5.1	164	38	44	22	0.01	28	1.4	21.2	61	0.01
KL16-01	363	366	0.84	8400	0.92	2.9	401	44	23	21	1	21	0.6	11.2	81	0.01
KL16-01	366	368	1.78	17800	2.08	6.8	185	90	32	19	3	33	1.2	38.0	48	0.01
KL16-01	368	369.6	1.66	16600	1.88	6.5	248	54	45	84	0.01	20	1.7	22.0	38	0.01
KL16-01	369.6	371	2.24	22400	2.39	6.6	142	37	280	81	5	40	1.3	28.0	61	0.01
KL16-01	371	373.2	1.09	10900	1.6	3	106	24	190	23	0.01	17	0.5	16.5	45	0.01
KL16-01	373.2	375	1.87	18700	1.77	1.4	170	14	28	42	0.01	22	0.3	29.0	30	0.01
KL16-01	375	378	0.83	8300	1.22	2.3	102	20	28	161	4	15	0.01	5.6	34	0.01
KL16-01	378	381	1.5	15000	1.82	2.8	140	20	59	74	9	12	0.2	21.0	36	0.01
KL16-01	381	384	1.5	15000	1.85	3.4	200	35	79	92	13	12	0.8	19.0	43	0.01
KL16-01	384	387	1.05	10500	1.22	2.8	143	37	47	78	7	13	0.01	20.0	32	0.01
KL16-01	387	390	1.62	16200	2.12	5.1	87	24	72	67	2	17	0.01	28.0	53	0.01
KL16-01	390	393	2.25	22500	2.62	2.8	250	25	26	50	5	62	1.2	48.0	80	0.01
KL16-01	393	396	1.08	10800	1.87	3	356	15	22	17	8	57	0.5	100.0	72	0.01
KL16-01	396	398.5	0.86	8600	2.36	2.9	2550	17	20	7	9	48	1.3	60.0	82	0.01
KL16-01	398.5	401.1	0.45	4500	1.33	1.1	1100	45	13	6	2	86	2.1	7.5	49	0.01
KL16-01	401.1	404.1	1.05	10500	1.46	2	630	25	4	85	0.01	60	0.3	27.5	21	0.01
KL16-01	404.1	406.5	0.2	2000	0.54	0.01	326	24	5	21	0.01	102	0.01	16.8	22	0.01
KL16-01	406.5	408.3	0.71	7100	1.23	1.2	314	31	4	530	0.01	125	0.01	13.4	32	0.01
KL16-01	408.3	411.3	0.75	7500	1.38	1.1	228	24	7	40	0.01	102	0.3	12.2	23	0.01
KL16-01	411.3	414.3	0.95	9500	1.48	1.1	263	25	8	100	0.01	82	0.3	15.6	35	0.01
KL16-01	414.3	417.2	2.2	22000	2.69	3.7	250	24	50	186	5	27	0.7	27.0	45	0.01
KL16-01	417.2	420	3.26	32600	2.57	7.2	200	14	63	286	3	31	0.6	32.0	48	0.01
KL16-01	420	421.5	2.05	20500	2.6	7.3	141	12	75	54	4	24	0.9	27.0	55	0.01
KL16-01	421.5	423.6	1.95	19500	1.88	3.1	373	12	210	114	1	27	4.1	31.0	44	0.01
KL16-01	423.6	426	0.158	1580	0.4	0.01	41	47	45	292	6	7	0.01	7.3	50	0.01
KL16-01	426	427.8	0.14	1400	0.36	1.3	1020	320	27	1100	4	8	3.3	5.4	43	0.01
KL16-01	427.8	430.4	0.0216	216	0.11	0.01	490	305	12	915	2	4	0.01	2.9	53	0.01
KL16-01	430.4	432.5	0.0283	283	0.08	0.7	1230	530	13	740	1	7	0.6	1.8	59	0.01
KL16-01	432.5	435	0.0326	326	0.05	0.01	214	94	3	118	0.01	6	0.01	1.3	116	0.01
KL16-01	435	438	0.0273	273	0.07	0.01	54	34	6	800	0.01	5	0.3	3.0	75	0.01
KL16-01	438	441	0.049	490	0.06	0.01	38	27	5	273	0.01	7	0.01	2.3	92	0.01
KL16-01	441	444	0.0374	374	0.04	0.01	174	26	8	199	0.01	5	0.01	2.0	95	0.01
KL16-01	444	446.4	0.0334	334	0.04	0.01	195	104	4	161	0.01	4	0.01	1.3	107	0.01
KL16-01	446.4	447.8	0.0126	126	0.02	0.01	34	36	9	64	2	6	0.01	1.2	58	0.01
KL16-01	447.8	450	0.0086	86	0.14	0.01	31	22	21	285	1	5	5.1	0.5	51	0.01
KL16-01	450	453	0.0051	51	0.01	0.01	530	250	10	136	0.01	3	0.3	0.0	50	0.01
KL16-01	453	456	0.0118	118	0.03	0.01	381	410	11	177	2	8	0.01	1.2	58	0.01
KL16-01	456	459	0.062	620	0.09	0.01	136	50	13	134	1	7	0.3	2.6	66	0.01
KL16-01	459	462	1.15	11500	0.61	3.5	178	28	28	15	1	74	0.7	4.0	53	0.01
KL16-01	462	468	0.99	9900	0.65	2.3	3300	120	89	150	0.01	25	0.5	13.5	43	0.01
KL16-01	468	477	0.072	720	0.05	0.01	114	21	8	9	0.01	7	0.01	1.7	14	0.01
KL16-01	477	480	0.0061	61	0.01	0.01	64	14	5	5	0.01	3	0.01	0.0	12	0.01
KL16-01	480	483	0.0064	64	0.01	0.01	116	27	6	6	0.01	4	0.5	0.6	14	0.01
KL16-01	483	489	0.002	20	0.01	0.01	39	21	3	6	0.01	2	0.01	0.0	17	0.01
KL16-02	0	2.9	0.62	6200	0.86	1.2	45	34	8	138	0.01	14	0.01	10.3	33	0.01
KL16-02	2.9	5.1	1.65	16500	1.08	1.7	52	30	19	178	0.01	20	0.01	18.0	27	0.01
KL16-02	5.1	7.4	0.93	9300	0.51	1.5	57	31	13	287	0.01	17	0.3	9.0	23	0.01
KL16-02	7.4	9.8	1.1	11000	0.57	1.1	45	32	27	156	0.01	16	0.2	15.5	20	0.01
KL16-02	9.8	11.9	0.79	7900	0.68	0.8	27	8	28	36	1	12	0.01	13.5	20	0.01
KL16-02	11.9	14.9	0.92	9200	1.08	1	94	14	39	342	0.01	10	0.01	10.0	22	0.01
KL16-02	14.9	17.9	1.57	15700	3.15	3	84	11	340	178	7	27	0.2	19.1	22	0.01
KL16-02	17.9	20.9	0.66	6600	1.24	0.9	104	13	30	630	0.01	16	0.3	9.8	34	0.01
KL16-02	20.9	23.9	0.422	4220	0.41	1.2	126	35	31	568	0.01	8	0.3	10.0	152	0.01
KL16-02	23.9	26.9	0.253	2530	0.36	1.1	121	14	14	545	0.01	11	0.4	5.8	106	0.01
KL16-02	26.9	29.9	0.352	3520	0.87	0.7	195	36	21	335	0.01	12	0.3	8.5	83	0.1
KL16-02	29.9	33	0.522	5220	0.72	1	225	44	27	1650	0.01	12	0.3	11.3	194	0.01
KL16-02	33	35.6	1.27	12700	2.43	4.1	4400	35	19	440	12	54	0.7	71.0	87	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL16-02	35.6	37	1.77	17700	2.73	6.2	1570	16	4	9	7	53	0.9	30.5	37	0.01
KL16-02	37	38.9	0.141	1410	0.13	3.3	4320	103	4	8	8	6	0.01	17.5	18	0.01
KL16-02	38.9	41.9	0.475	4750	0.37	1.8	2250	46	9	82	3	15	0.01	10.0	42	0.01
KL16-02	41.9	44.9	0.1	1000	0.4	4.8	2400	780	9	5	25	4	0.01	18.8	27	0.01
KL16-02	44.9	47.4	0.41	4100	0.57	2.6	12200	95	20	90	13	12	0.3	37.3	29	0.01
KL16-02	47.4	49.4	0.7	7000	0.8	3.7	20400	61	18	13	10	30	0.3	70.0	57	0.01
KL16-02	49.4	52.4	0.288	2880	1.02	3.6	11400	139	24	8	20	16	0.01	46.8	36	0.01
KL16-02	52.4	55.4	0.504	5040	0.93	5.5	33700	470	21	5	24	28	0.01	73.8	50	0.01
KL16-02	55.4	57.5	0.73	7300	1.25	17.2	26700	3100	10	19	68	17	0.5	114.0	56	0.01
KL16-02	57.5	59.9	0.74	7400	0.71	3.6	1360	58	10	206	1	76	0.01	12.3	60	0.01
KL16-02	59.9	62.9	2.08	20800	1.2	4.4	373	45	7	274	1	52	0.01	21.3	83	0.01
KL16-02	62.9	65.4	1.13	11300	0.75	2.4	368	16	6	143	0.01	66	0.01	14.8	96	0.01
KL16-02	65.4	68.4	6.85	68500	4.34	15	1280	148	16	397	1	68	0.4	37.5	135	0.4
KL16-02	68.4	70.4	1.92	19200	0.57	4.5	530	268	20	215	1	24	1.1	11.4	44	0.13
KL16-02	70.4	73.4	1.03	10300	0.35	3	268	56	19	382	1	17	0.01	9.3	93	0.01
KL16-02	73.4	76.4	2.4	24000	1.1	6.9	59	36	4	465	1	20	0.2	15.2	102	0.13
KL16-02	76.4	79.4	1.83	18300	0.87	4.4	94	47	15	470	2	16	0.2	11.5	144	0.01
KL16-02	79.4	82.4	2.2	22000	0.87	4.6	117	40	3	350	2	17	0.01	22.5	67	0.01
KL16-02	82.4	85.4	2.39	23900	0.71	5.3	72	40	35	258	1	14	0.2	13.8	58	0.1
KL16-02	85.4	88.4	0.83	8300	0.32	2.5	61	11	14	495	0.01	20	0.2	9.7	78	0.01
KL16-02	88.4	91.4	1.65	16500	0.7	3.5	84	32	21	357	0.01	23	0.4	16.0	113	0.01
KL16-02	91.4	94.4	2.17	21700	3.48	4.1	54	49	21	5750	1	46	0.01	15.0	98	0.01
KL16-02	94.4	97.4	2.43	24300	1.13	1.9	55	27	10	918	0.01	45	0.2	20.6	122	0.01
KL16-02	97.4	100.4	1.49	14900	2.09	2.1	85	26	6	307	1	57	0.01	11.2	57	0.01
KL16-02	100.4	103.4	2.88	28800	2.17	3.8	203	43	24	197	0.01	62	0.01	20.0	136	0.01
KL16-02	103.4	106.4	1.95	19500	1.65	3.9	410	13	19	258	0.01	80	0.01	12.5	86	0.01
KL16-02	106.4	109.4	0.467	4670	0.48	1.5	1200	16	9	27	2	49	0.01	19.9	123	0.01
KL16-02	109.4	112.4	3.42	34200	0.96	11.5	143	14	8	5	8	38	0.01	5.0	21	0.01
KL16-02	112.4	115.4	2.07	20700	2.13	3.9	9200	20	20	48	0.01	119	0.5	52.5	100	0.01
KL16-02	115.4	118.4	0.154	1540	0.79	0.9	257	14	12	26	0.01	42	0.4	12.8	78	0.01
KL16-02	118.4	121.4	2.21	22100	0.93	5.5	4900	16	23	3	1	118	0.01	16.0	78	0.01
KL16-02	121.4	124.4	0.95	9500	2.52	2	790	41	53	3	0.01	49	0.7	37.1	61	0.01
KL16-02	124.4	125.9	5.2	52000	3.05	11.2	670	20	30	88	0.01	135	0.6	57.6	67	0.01
KL16-02	125.9	128.2	0.241	2410	0.96	1.5	1260	12	48	22	0.01	23	0.5	31.0	74	0.01
KL16-02	128.2	130.4	0.77	7700	1.17	2.9	34200	13	59	74	6	61	2.2	62.5	76	0.01
KL16-02	130.4	133.4	0.955	9550	0.96	2	24700	10	67	155	6	62	4.7	52.5	101	0.01
KL16-02	133.4	135.4	0.65	6500	0.91	3.3	19800	15	130	15	26	65	5.1	35.0	42	0.01
KL16-02	135.4	137.2	0.403	4030	0.69	2.9	1470	353	110	15	2	14	2.6	4.8	31	0.01
KL16-02	137.2	139.1	0.0206	206	0.14	1.5	790	1430	26	2	1	2	1.3	3.3	19	0.01
KL16-02	139.1	140.9	0.0305	305	0.1	1.4	760	620	15	0.01	0.01	3	2.1	1.3	21	0.01
KL16-02	140.9	143.9	0.0135	135	0.07	1.1	760	490	19	3	0.01	3	2.2	1.5	23	0.01
KL16-02	143.9	146.9	0.0189	189	0.1	1.2	860	660	15	10	0.01	2	4.1	0.8	22	0.01
KL16-02	146.9	149.9	0.0159	159	0.03	0.9	363	317	9	2	0.01	3	1.9	0.5	19	0.01
KL16-02	149.9	152.9	0.0065	65	0.01	2.7	500	1390	4	8	0.01	0.01	6.2	0.5	16	0.01
KL16-02	152.9	155.9	0.0064	64	0.01	0.01	135	29	4	0.01	0.01	0.01	0.01	0.5	20	0.01
KL16-02	155.9	158.9	0.011	110	0.01	0.01	63	20	1	0.01	0.01	17	0.01	0.0	16	0.01
KL16-02	158.9	161.9	0.0111	111	0.01	1	1220	820	6	5	0.01	4	3.3	2.3	19	0.01
KL16-03	0	5.5	0.72	7200	0.57	1.1	100	23	11	108	1	11	0.5	12.2	38	0.01
KL16-03	5.5	8.5	0.78	7800	0.81	1.4	106	27	8	149	1	11	0.3	9.1	12	0.01
KL16-03	8.5	11.5	0.75	7500	0.57	1.3	107	17	7	92	1	13	0.01	6.0	25	0.01
KL16-03	11.5	14.5	1.41	14100	1.54	2	88	32	7	54	0.01	16	0.01	14.5	15	0.01
KL16-03	14.5	17.5	0.471	4710	0.49	1	343	24	9	196	0.01	11	0.2	4.8	15	0.01
KL16-03	17.5	20.5	0.68	6800	0.68	1.2	324	68	110	113	1	11	0.2	3.0	14	0.01
KL16-03	20.5	23.5	0.98	9800	1.14	1.5	381	43	17	120	1	18	0.4	8.0	25	0.01
KL16-03	23.5	26	1.02	10200	1.24	1	147	68	38	118	1	20	0.6	28.7	30	0.01
KL16-03	26	32	1.25	12500	1.78	2.7	140	27	28	435	1	13	0.4	9.4	72	0.01
KL16-03	32	34.6	0.502	5020	0.86	1.1	1000	33	31	224	1	8	0.4	10.2	82	0.01
KL16-03	34.6	36.5	3.48	34800	0.62	5.1	1050	18	12	600	2	46	0.2	14.0	124	0.01
KL16-03	36.5	38.5	0.6	6000	0.87	0.8	700	10	6	22	1	25	0.01	13.0	28	0.01
KL16-03	38.5	41.5	0.65	6500	1	1.5	38500	50	16	54	5	87	1.6	74.5	79	0.01
KL16-03	41.5	43.6	0.49	4900	1.05	4.5	18700	50	36	7	14	52	5.6	35.5	39	0.01
KL16-03	43.6	46.4	0.051	510	0.11	4.8	2690	750	18	10	15	3	0.6	18.6	19	0.01
KL16-03	46.4	47.5	0.059	590	0.18	7.3	2300	390	16	25	13	4	1	15.8	37	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL16-03	47.5	50.5	0.2	2000	0.25	3.9	4900	790	27	13	15	8	0.6	27.5	36	0.01
KL16-03	50.5	53.5	0.276	2760	0.31	10.8	4330	184	20	11	8	12	0.7	19.3	45	0.01
KL16-03	53.5	56.5	0.31	3100	1.07	10.3	12100	840	32	12	10	8	0.5	28.0	43	0.01
KL16-03	56.5	59.5	0.59	5900	4.6	12.9	63000	2450	35	11	60	42	0.01	86.3	70	0.01
KL16-03	59.5	62.5	0.97	9700	3.91	9.2	6300	106	54	22	18	20	0.6	64.4	175	0.01
KL16-03	62.5	65.5	1.91	19100	1.49	6.1	840	170	22	59	2	27	0.8	24.5	120	0.01
KL16-03	65.5	68.5	0.67	6700	0.62	19.3	19000	2300	35	225	32	27	1.2	50.0	73	0.01
KL16-03	68.5	71.5	0.59	5900	1.47	72.3	52400	18000	39	176	270	46	3.1	140.0	120	0.01
KL16-03	71.5	74.5	0.0206	206	0.2	5.9	1990	5400	33	5	8	3	1.7	16.1	11	0.01
KL16-03	74.5	77.5	0.0371	371	0.21	19.9	7500	8400	36	18	52	0.01	3.9	22.8	22	0.01
KL16-03	77.5	83.5	0.113	1130	0.31	31.2	12400	17600	89	12	94	8	5	72.3	33	0.01
KL16-03	83.5	86.5	0.131	1310	0.3	26.4	11100	14400	59	13	74	8	4.3	52.8	36	0.01
KL16-03	86.5	89.5	0.0063	63	0.19	1.6	1220	303	50	5	19	2	1.2	8.3	21	0.01
KL16-03	89.5	92.5	0.0042	42	0.17	1.6	570	185	38	10	11	2	1.1	2.5	15	0.01
KL16-03	92.5	95.5	0.0207	207	0.2	1.9	840	285	38	10	7	3	1.5	3.3	15	0.01
KL16-03	95.5	98.3	0.0262	262	0.15	6.9	4290	1590	33	0.01	16	4	5.8	6.8	38	0.01
KL16-03	98.3	100.7	0.168	1680	2.59	15.1	9800	1940	260	44	58	12	19.6	37.9	90	0.01
KL16-03	100.7	102.6	0.0075	75	0.21	0.01	272	41	26	2	2	2	1.2	2.4	22	0.01
KL16-03	102.6	104.5	0.0147	147	0.07	0.01	198	51	20	2	1	2	0.4	1.0	16	0.01
KL16-03	104.5	107.1	0.0067	67	0.05	0.01	175	110	27	0.01	1	3	0.9	0.9	14	0.01
KL16-03	107.1	110.2	0.0105	105	0.04	0.01	750	57	23	3	0.01	3	0.4	2.5	16	0.01
KL16-03	110.2	113.3	0.006	60	0.02	0.01	158	26	11	0.01	0.01	3	0.7	0.9	14	0.01
KL16-03	113.3	116.5	0.0017	17	0.02	0.01	53	23	9	0.01	0.01	0.01	0.3	0.7	14	0.01
KL16-03	116.5	117.9	0.0032	32	0.1	0.01	133	84	31	0.01	0.01	2	1.2	3.3	16	0.01
KL16-03	117.9	120.9	0.0092	92	0.04	0.01	118	35	16	0.01	0.01	0.01	0.8	0.6	15	0.01
KL16-03	120.9	124	0.0028	28	0.02	0.01	73	54	8	0.01	1	0.01	0.5	0.6	14	0.01
KL16-03	124	127	0.0004	4	0.01	0.01	210	57	10	0.01	0.01	0.01	0.8	0.7	13	0.01
KL16-03	127	130.1	0.0123	123	0.03	0.01	321	61	10	0.01	0.01	0.01	1.1	1.2	18	0.01
KL16-03	130.1	132.4	0.0006	6	0.04	0.01	294	119	7	0.01	0.01	0.01	1.1	2.3	16	0.01
KL16-03	132.4	134.5	0.0003	3	0.01	0.01	129	48	3	0.01	0.01	0.01	0.4	0.0	17	0.01
KL16-03	134.5	137.5	0.0004	4	0.01	0.01	124	72	3	0.01	0.01	0.01	0.4	0.0	13	0.01
KL16-03	137.5	140.5	0.0005	5	0.01	0.01	166	54	7	4	0.01	0.01	0.5	0.7	17	0.01
KL16-03	140.5	143.5	0.0008	8	0.02	0.01	317	100	7	9	0.01	0.01	0.6	2.1	18	0.01
KL16-03	143.5	146.5	0.0013	13	0.01	0.01	176	48	2	0.01	0.01	0.01	0.01	0.9	21	0.01
KL16-03	146.5	149.5	0.037	370	0.03	0.01	2050	38	4	0.01	40	4	0.5	2.6	13	0.01
KL16-03	149.5	152.5	0.0031	31	0.01	0.01	162	39	6	0.01	1	0.01	0.01	0.0	12	0.01
KL16-03	152.5	155.5	0.0004	4	0.01	0.01	111	20	0.01	0.01	0.01	0.01	0.4	0.0	12	0.01
KL16-03	155.5	158.5	0.004	40	0.01	0.01	500	161	6	0.01	0.01	3	0.9	0.7	11	0.01
KL16-03	158.5	161.5	0.0011	11	0.01	0.01	500	75	7	3	0.01	0.01	1.1	0.0	11	0.01
KL16-03	161.5	164.5	0.0038	38	0.01	0.01	335	45	14	15	1	0.01	0.3	1.0	12	0.01
KL16-03	164.5	167.5	0.0056	56	0.01	0.6	540	64	15	37	2	0.01	2	0.7	16	0.01
KL16-03	167.5	170.5	0.0296	296	0.01	0.01	356	34	7	69	1	4	1.1	1.4	13	0.01
KL16-03	170.5	173.5	0.0097	97	0.01	0.01	170	48	8	9	1	3	0.5	0.9	13	0.01
KL16-03	173.5	176.5	0.0044	44	0.01	0.01	255	21	19	9	1	5	0.3	0.7	13	0.01
KL16-03	176.5	179.5	0.0071	71	0.06	0.01	410	60	67	75	2	5	2.2	2.9	24	0.1
KL16-03	179.5	182.5	0.0054	54	0.2	0.01	240	23	110	19	1	3	5.6	4.1	24	0.2
KL16-03	182.5	185.5	0.0086	86	0.13	0.01	700	48	130	33	2	3	5	6.5	21	0.25
KL16-03	185.5	188.5	0.0055	55	0.26	0.01	264	25	140	21	2	9	7.4	5.9	25	0.17
KL16-03	188.5	191.5	0.0153	153	0.4	0.01	163	17	200	26	2	6	5.4	0.8	29	0.17
KL16-04	0	2.3	0.58	5800	0.92	0.9	40	11	16	17	2	11	0.2	6.5	22	0.01
KL16-04	2.3	5.2	1.21	12100	2.39	1.7	100	49	13	238	1	20	0.4	14.8	8	0.01
KL16-04	5.2	8.2	0.95	9500	0.81	1.2	118	40	9	96	0.01	8	0.3	10.3	17	0.01
KL16-04	8.2	11.2	0.63	6300	0.6	0.8	134	39	3	1400	0.01	7	0.01	8.7	32	0.01
KL16-04	11.2	14.2	0.78	7800	0.74	0.8	157	27	4	164	1	10	0.3	6.8	14	0.01
KL16-04	14.2	17.2	0.432	4320	0.36	0.01	174	78	4	457	0.01	3	0.01	4.0	12	0.01
KL16-04	17.2	20.2	0.339	3390	0.34	0.01	147	45	4	220	0.01	4	0.01	3.0	69	0.01
KL16-04	20.2	22.3	0.472	4720	0.49	1	136	33	5	550	0.01	8	0.01	6.1	98	0.01
KL16-04	22.3	25.5	0.435	4350	0.36	0.9	85	24	1	590	0.01	5	0.01	2.5	58	0.01
KL16-04	25.5	28.6	0.496	4960	0.53	1.4	213	62	4	670	0.01	4	0.01	5.0	24	0.01
KL16-04	28.6	31.6	0.79	7900	0.73	1	212	12	20	201	0.01	8	0.01	7.8	18	0.01
KL16-04	31.6	34.6	0.83	8300	0.84	0.9	67	13	25	213	0.01	14	1.2	12.5	12	0.01
KL16-04	34.6	36.1	1.6	16000	1.69	2.1	96	27	11	910	0.01	11	0.01	11.3	24	0.01
KL16-04	36.1	38.2	0.87	8700	1.13	1.5	65	38	10	180	0.01	8	0.2	10.0	80	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL16-04	38.2	41.2	0.74	7400	0.79	1.2	274	21	28	154	0.01	25	0.3	16.1	14	0.01
KL16-04	41.2	44.2	0.86	8600	1.04	1.1	65	17	18	590	1	8	0.3	8.3	34	0.01
KL16-04	44.2	46.4	1.64	16400	2.16	2	127	29	13	202	2	18	0.3	16.3	23	0.01
KL16-04	46.4	49.1	1.07	10700	0.87	0.8	380	12	37	264	0.01	88	0.2	23.0	21	0.01
KL16-04	49.1	51.6	1.15	11500	1.41	1.7	82	11	13	52	1	16	0.4	10.0	31	0.01
KL16-04	51.6	53.5	1.44	14400	1.76	2.9	128	11	21	760	1	12	0.4	12.8	33	0.01
KL16-04	53.5	67.1	0.428	4280	0.79	1.3	134	37	33	2710	4	7	0.4	15.2	29	0.01
KL16-04	67.1	70.3	1.54	15400	1.23	2.6	550	17	38	82	8	34	2.3	26.1	42	0.01
KL16-04	70.3	71.8	1.05	10500	1.73	3.7	540	43	31	2800	10	27	0.3	19.5	64	0.01
KL16-04	71.8	73.7	0.83	8300	1.33	3	9900	44	18	1280	44	33	0.3	38.0	52	0.01
KL16-04	73.7	75.3	0.0346	346	0.28	0.01	183	38	35	5080	5	6	0.01	12.8	105	0.01
KL16-04	75.3	77.2	0.0205	205	0.39	0.01	265	42	44	2560	5	5	0.01	3.5	51	0.01
KL16-04	77.2	80.2	0.03	300	0.85	1	980	56	36	146	2	3	0.6	1.5	37	0.01
KL16-04	80.2	83.2	0.168	1680	0.67	3.3	7900	119	30	37	5	7	1.9	11.3	36	0.01
KL16-04	83.2	86.2	0.102	1020	1.67	38.1	7600	13500	19	44	178	4	3.9	102.5	37	0.01
KL16-04	86.2	89.2	0.0207	207	0.16	4.5	390	930	13	42	14	3	0.4	16.0	18	0.01
KL16-04	89.2	92.2	0.0212	212	0.21	4.2	3440	750	16	375	18	3	0.8	9.8	22	0.01
KL16-04	92.2	95.2	0.0349	349	0.96	7	3990	3290	31	27	9	2	1.8	19.8	36	0.01
KL16-04	95.2	97.9	0.0173	173	1.05	10	4780	2450	32	56	48	4	1.5	26.6	46	0.01
KL16-04	97.9	100.9	0.0064	64	0.16	3	1350	640	20	53	16	0.01	0.6	11.1	32	0.01
KL16-04	100.9	103.9	0.0028	28	0.12	2.5	680	630	29	19	9	2	0.9	4.8	25	0.01
KL16-04	103.9	107	0.0106	106	0.13	3.2	1470	1370	33	28	12	3	1	8.5	52	0.01
KL16-04	107	109.9	0.0103	103	0.24	11.1	7800	4400	22	38	47	4	0.01	53.0	24	0.01
KL16-04	109.9	112.6	0.004	40	0.09	1.5	680	430	26	10	9	2	0.4	4.8	13	0.01
KL16-04	112.6	115.7	0.0081	81	0.14	3.3	3940	860	21	12	18	2	0.6	8.8	19	0.01
KL16-04	115.7	118.8	0.0072	72	0.07	2.4	1370	1540	23	21	1	3	1.2	8.0	35	0.01
KL16-04	118.8	121.8	0.0089	89	0.08	2.6	2430	1800	26	20	4	2	0.7	11.0	32	0.01
KL16-04	121.8	124.9	0.0223	223	0.17	4.8	3650	2260	38	99	18	3	1.2	20.0	36	0.01
KL16-04	124.9	128	0.0206	206	0.17	5.5	8300	1530	45	15	28	0.01	1.7	27.1	31	0.01
KL16-04	128	131	0.0187	187	0.12	5.5	5700	950	40	56	26	0.01	0.8	25.0	36	0.01
KL16-04	131	134.2	0.065	650	0.13	2.8	3820	580	110	14	11	0.01	2	19.0	18	0.01
KL16-04	134.2	136.4	0.017	170	0.09	1.2	1660	238	33	26	5	0.01	0.7	8.8	20	0.01
KL16-04	136.4	139.1	0.0041	41	0.04	0.01	264	80	12	14	0.01	0.01	0.4	1.8	21	0.01
KL16-04	139.1	142.3	0.0038	38	0.03	0.01	251	137	12	34	0.01	0.01	0.2	2.3	21	0.01
KL16-04	142.3	145.3	0.0023	23	0.02	0.6	232	280	9	7	0.01	0.01	0.01	1.3	14	0.01
KL16-04	145.3	147.3	0.0048	48	0.03	0.01	260	162	12	24	1	2	0.4	1.8	17	0.01
KL16-04	147.3	149.2	0.0123	123	0.05	1	990	255	28	81	2	0.01	0.8	2.0	15	0.01
KL16-04	149.2	152.2	0.0325	325	0.12	8.7	4750	8900	37	129	23	0.01	2.9	61.6	19	0.01
KL16-04	152.2	155.2	0.0066	66	0.07	1.4	800	160	20	7	5	0.01	0.7	5.0	22	0.01
KL16-04	155.2	157.6	0.013	130	0.07	1.7	1440	1140	30	6	4	0.01	1.2	20.6	23	0.01
KL16-04	157.6	164.2	0.0042	42	0.04	0.9	329	143	29	5	0.01	0.01	0.8	2.3	20	0.01
KL16-04	164.2	176.2	0.0366	366	0.7	18	6900	3600	130	120	36	4	4.9	27.3	67	0.23
KL16-04	176.2	182.2	0.0068	68	0.31	3.8	550	590	49	45	7	2	2	10.0	61	0.11
KL16-04	182.2	185.2	0.001	10	0.06	1.2	117	135	18	3	2	0.01	0.8	0.0	20	0.01
KL16-04	185.2	188.2	0.001	10	0.05	0.01	235	78	24	0.01	0.01	0.01	0.7	0.0	21	0.01
KL16-04	188.2	191.2	0.0133	133	0.04	0.01	73	45	13	5	0.01	0.01	0.3	0.0	22	0.01
KL16-05	0	2.2	1.89	18900	1.81	1.5	115	29	10	1720	1	18	0.3	12.3	29	0.01
KL16-05	2.2	5.2	1.21	12100	1.43	0.7	76	17	23	202	1	12	0.01	14.5	25	0.01
KL16-05	5.2	7.6	0.63	6300	0.68	0.8	194	52	9	430	1	13	0.4	12.8	48	0.01
KL16-05	7.6	10.6	0.61	6100	0.72	0.6	460	42	14	220	0.01	10	0.3	11.5	18	0.01
KL16-05	10.6	13.6	0.494	4940	0.52	0.6	168	41	4	590	0.01	10	0.5	8.5	31	0.01
KL16-05	13.6	16.7	0.76	7600	0.83	0.6	82	19	9	138	0.01	11	0.3	11.1	23	0.01
KL16-05	16.7	20.2	1.02	10200	1.65	0.8	201	32	37	109	0.01	15	0.5	16.3	17	0.01
KL16-05	20.2	22.4	0.64	6400	1.2	0.6	63	22	6	244	0.01	14	0.2	13.0	16	0.01
KL16-05	22.4	25.5	1.03	10300	1.63	0.9	225	46	9	127	3	9	0.2	10.0	18	0.01
KL16-05	25.5	28.6	0.76	7600	0.93	0.7	195	28	4	59	1	10	0.01	11.8	33	0.01
KL16-05	28.6	31.7	1.56	15600	2.18	1.2	168	15	26	88	1	18	0.01	10.0	10	0.01
KL16-05	31.7	34.8	0.92	9200	1.12	0.9	274	19	10	132	0.01	13	0.01	15.8	11	0.01
KL16-05	34.8	38.2	1.02	10200	1.18	1.5	810	68	23	230	1	16	0.2	14.1	19	0.01
KL16-05	38.2	41.2	0.473	4730	0.72	0.01	79	23	10	91	0.01	11	0.01	8.8	17	0.01
KL16-05	41.2	44.2	0.352	3520	0.41	0.01	76	23	11	112	0.01	9	0.5	6.3	30	0.01
KL16-05	44.2	47.2	0.327	3270	0.31	0.01	73	17	7	21	0.01	6	0.2	5.8	35	0.01
KL16-05	47.2	49.4	0.406	4060	0.49	0.01	500	39	8	93	1	16	0.01	8.3	18	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL16-05	49.4	52.4	0.76	7600	0.71	0.9	2030	40	26	68	0.01	63	0.4	24.2	15	0.01
KL16-05	52.4	55.4	1.48	14800	1.51	1.8	12200	32	16	63	1	92	0.6	24.4	43	0.01
KL16-05	55.4	57	0.61	6100	1.27	0.8	395	40	8	8	2	9	0.01	9.0	27	0.01
KL16-05	57	59.2	0.29	2900	0.51	0.5	430	18	3	84	0.01	4	0.01	5.3	24	0.01
KL16-05	59.2	62.6	0.312	3120	0.37	0.01	129	13	6	136	2	6	0.01	5.3	17	0.01
KL16-05	62.6	65.2	1.82	18200	2.28	2.3	140	12	22	160	2	24	0.01	12.1	35	0.01
KL16-05	65.2	68.2	0.91	9100	1.57	1.1	84	12	30	82	5	13	0.01	16.3	13	0.01
KL16-05	68.2	71.2	0.7	7000	1.19	1	212	20	17	134	3	13	0.3	13.6	20	0.01
KL16-05	71.2	74.2	0.391	3910	0.59	0.01	145	22	3	315	3	10	0.3	6.3	32	0.01
KL16-05	74.2	77.2	0.345	3450	0.47	0.01	131	59	26	64	2	16	0.4	8.3	20	0.01
KL16-05	77.2	80.2	0.58	5800	0.56	0.7	103	22	12	173	2	21	0.3	13.8	30	0.01
KL16-05	80.2	83.2	0.35	3500	0.34	0.5	119	31	1	450	0.01	6	0.01	6.0	31	0.01
KL16-05	83.2	84.7	0.81	8100	0.78	0.9	110	27	18	369	0.01	17	1.1	10.4	26	0.01
KL16-05	84.7	101.2	0.397	3970	0.53	0.9	77	33	10	131	0.01	9	1	4.5	20	0.01
KL16-05	101.2	110.2	0.86	8600	0.53	0.9	109	21	36	190	1	12	1.5	12.5	14	0.01
KL16-05	110.2	116.2	0.75	7500	0.76	1.3	287	25	12	655	2	20	0.9	10.6	41	0.01
KL16-05	116.2	122.2	0.343	3430	0.42	0.6	68	19	11	93	2	17	0.01	6.8	14	0.01
KL16-05	122.2	126.6	0.41	4100	0.53	0.7	56	12	14	324	1	21	0.2	8.5	23	0.01
KL16-05	126.6	129.2	0.215	2150	0.21	0.01	126	23	4	30	2	17	0.01	7.3	80	0.01
KL16-05	129.2	131.6	0.096	960	0.16	0.01	90	28	9	810	2	8	0.01	4.5	37	0.01
KL16-05	131.6	134.1	0.347	3470	0.52	0.7	134	41	55	79	2	51	0.8	12.8	21	0.01
KL16-05	134.1	137.2	0.113	1130	0.19	0.01	198	11	11	14	132	16	0.4	8.0	14	0.01
KL16-05	137.2	138.9	0.303	3030	0.16	0.9	600	26	68	16	2	379	0.5	45.5	23	0.01
KL16-05	138.9	142.2	0.058	580	0.05	0.8	1490	118	37	82	4	22	0.8	6.3	18	0.01
KL16-05	142.2	145.2	0.071	710	0.09	0.8	14500	31	47	22	5	50	2.1	16.3	20	0.01
KL16-05	145.2	148.2	0.052	520	0.22	0.01	10300	41	34	21	5	14	0.8	9.5	21	0.01
KL16-05	148.2	150.4	0.0371	371	0.34	0.01	6300	20	16	6	2	8	0.6	5.0	20	0.01
KL16-05	150.4	152.2	0.42	4200	0.97	3.7	94600	103	37	34	8	82	0.5	82.0	34	0.01
KL16-05	152.2	155.2	0.06	600	0.71	1	4000	25	23	166	200	10	0.5	9.2	30	0.1
KL16-05	155.2	158.2	0.076	760	5.76	1.3	6820	44	42	93	38	25	0.6	14.0	31	0.01
KL16-05	158.2	161.2	0.0286	286	13.8	2.3	460	32	37	30	8	6	0.3	1.3	26	0.01
KL16-05	161.2	163.7	0.0385	385	3.09	1.6	820	138	54	44	53	7	1.1	5.3	33	0.01
KL16-05	163.7	165.2	0.113	1130	0.44	3.2	3300	260	18	58	3	6	0.6	6.0	17	0.01
KL16-05	165.2	167.2	0.112	1120	0.51	1.7	21100	125	42	8	7	18	0.9	17.3	23	0.01
KL16-05	167.2	170.2	0.0262	262	0.29	0.8	3730	59	27	59	3	5	0.6	5.3	19	0.01
KL16-05	170.2	173.2	0.163	1630	0.65	5	16400	520	100	156	20	10	1.3	20.7	227	0.01
KL16-05	173.2	175.5	0.081	810	0.56	1.2	5700	104	69	37	2	6	0.6	11.8	40	0.01
KL16-05	175.5	177.7	0.0255	255	0.38	1.8	3060	197	95	25	10	3	2.6	8.0	46	0.01
KL16-05	177.7	180.2	0.0042	42	0.13	1.8	470	287	29	9	12	2	0.5	3.5	36	0.01
KL16-05	180.2	181.9	0.0041	41	0.18	1.4	610	520	26	10	30	0.01	0.6	5.5	42	0.01
KL16-05	181.9	184.3	0.068	680	0.11	0.8	450	650	14	12	2	0.01	0.5	6.5	35	0.01
KL16-05	184.2	187.3	0.06	600	0.17	9.1	3440	2320	50	12	46	2	0.6	22.8	51	0.01
KL16-05	187.3	190	0.0223	223	0.11	6.3	4780	1870	32	48	22	3	1.1	13.8	27	0.01
KL16-05	190	193.2	0.0162	162	0.1	1.8	1300	198	51	88	7	2	0.6	7.3	23	0.01
KL16-05	193.2	196.3	0.0119	119	0.1	1.7	1160	124	44	64	6	3	0.2	7.5	25	0.01
KL16-05	196.3	199.3	0.043	430	0.1	5.9	3880	3100	33	41	16	0.01	1.6	13.8	26	0.01
KL16-05	199.3	202.3	0.194	1940	0.49	51.5	29500	25200	70	156	89	3	26	47.9	58	0.01
KL16-05	202.3	205.2	0.133	1330	0.34	59.5	46600	55000	40	97	60	5	63	211.0	62	0.01
KL16-05	205.2	209.2	0.067	670	0.12	20.1	7200	8600	40	36	30	3	14.3	32.0	31	0.01
KL16-05	209.2	211.5	0.0214	214	0.12	8	2900	3020	41	34	13	3	30	9.1	23	0.01
KL16-05	211.5	212.7	0.023	230	0.24	15.7	3860	4920	100	41	8	2	50	15.7	56	0.01
KL16-05	212.7	218.2	0.013	130	0.18	2.4	1070	640	59	207	2	3	3.7	4.8	51	0.01
KL16-06	0	3	1.02	10200	0.94	1.2	74	55	17	317	0.01	13	0.5	10.3	53	0.01
KL16-06	3	6	0.71	7100	0.78	0.9	92	52	18	600	0.01	18	0.7	12.2	38	0.01
KL16-06	6	9	1.04	10400	0.66	0.7	81	47	17	460	1	15	0.4	14.3	43	0.01
KL16-06	9	11.1	0.78	7800	0.83	0.8	58	33	32	620	4	11	0.2	12.5	35	0.01
KL16-06	11.1	13	1.29	12900	1.68	1.6	62	25	40	75	2	20	0.01	16.1	27	0.01
KL16-06	13	15.7	1.48	14800	2.33	2	150	87	720	110	1	37	3.2	20.0	77	0.01
KL16-06	15.7	18	0.487	4870	0.77	0.8	149	29	150	395	0.01	15	2.5	12.3	84	0.01
KL16-06	18	21	0.84	8400	0.91	1	194	21	16	770	0.01	17	1.3	15.5	64	0.01
KL16-06	21	24	0.62	6200	0.85	1.2	470	91	120	920	0.01	15	0.8	21.8	83	0.01
KL16-06	24	27	0.62	6200	1.02	1.1	175	24	16	310	0.01	13	0.7	8.8	30	0.01
KL16-06	27	30	0.48	4800	0.68	1.7	406	241	18	650	0.01	16	0.6	18.8	102	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL16-06	30	33	0.321	3210	0.96	1	175	160	95	690	1	5	1.3	17.0	170	0.01
KL16-06	33	36	0.61	6100	3.78	1.6	290	42	240	530	0.01	16	5.1	12.5	44	0.14
KL16-06	36	39	0.99	9900	2.46	2.1	334	66	28	114	0.01	22	0.9	49.2	50	0.01
KL16-06	39	42	0.6	6000	1.49	1.7	375	38	34	24	0.01	14	0.5	35.0	31	0.01
KL16-06	42	45	1.06	10600	1.55	2.2	490	22	13	12	0.01	29	0.3	40.0	47	0.01
KL16-06	45	48	0.7	7000	0.51	2.4	16300	22	12	5	1	39	1.4	35.9	27	0.01
KL16-06	48	51	0.47	4700	0.77	1.5	17200	24	8	15	3	42	3.2	50.0	28	0.01
KL16-06	51	54	0.98	9800	1.55	2.4	6200	22	8	20	2	33	0.7	55.0	80	0.01
KL16-06	54	56.5	3.22	32200	1.73	6.5	3900	34	10	77	0.01	35	0.4	57.0	77	0.01
KL16-06	56.5	58.5	1.03	10300	1.5	2.5	136	19	4	4	1	11	0.01	4.8	9	0.01
KL16-06	58.5	61.5	1.82	18200	1.37	1.7	273	19	1	263	0.01	35	0.2	14.0	64	0.01
KL16-06	61.5	64.5	0.82	8200	0.84	0.9	223	40	8	388	0.01	46	1.1	35.0	52	0.01
KL16-06	64.5	67.5	0.72	7200	0.72	0.8	372	29	5	169	0.01	40	0.7	17.3	59	0.12
KL16-06	67.5	70.5	1.42	14200	2.82	1.7	830	26	2	153	1	37	0.8	9.0	76	0.01
KL16-06	70.5	73.5	2.13	21300	3.36	2.9	600	22	3	276	5	34	0.3	13.5	49	0.01
KL16-06	73.5	76.5	5.6	56000	7.68	7.4	299	130	25	240	4	22	1.7	30.0	105	0.01
KL16-06	76.5	79.5	0.55	5500	0.24	1.2	240	101	48	315	1	14	2.6	7.5	72	0.01
KL16-06	79.5	81.5	3.87	38700	2.6	7.2	132	49	25	367	3	20	1.2	18.0	81	0.01
KL16-06	81.5	84	2.34	23400	1.34	7.7	124	173	38	194	2	11	1.4	12.5	68	0.12
KL16-06	84	87	1.8	18000	0.55	4.3	49	45	10	110	3	10	0.3	9.5	80	0.01
KL16-06	87	90	1.63	16300	0.59	3.5	55	26	8	111	2	7	0.3	10.0	60	0.01
KL16-06	90	93	0.85	8500	0.32	1.6	24	14	6	79	1	3	0.2	6.3	52	0.01
KL16-06	93	96	1.2	12000	0.39	2	45	20	6	17	1	5	0.01	4.8	56	0.01
KL16-06	96	99	2.07	20700	0.41	3.8	56	20	11	37	3	8	0.2	6.0	42	0.01
KL16-06	99	102	1.63	16300	0.4	2.7	26	18	9	32	3	7	0.2	7.0	50	0.01
KL16-06	102	105	1.6	16000	0.65	3.3	45	18	11	17	3	8	1	8.9	67	0.01
KL16-06	105	108	0.83	8300	0.64	2.1	50	23	34	26	4	11	0.01	13.3	52	0.01
KL16-06	108	111	1.1	11000	0.59	1.8	60	22	11	32	2	8	0.01	15.5	38	0.01
KL16-06	111	114	1.42	14200	0.81	2.9	75	25	8	17	5	7	0.01	10.3	36	0.01
KL16-06	114	117	1.29	12900	1.92	3.1	253	193	38	84	4	10	0.9	25.0	47	0.01
KL16-06	117	120	1.6	16000	2.23	3.2	141	87	34	82	3	11	1.4	22.3	46	0.01
KL16-06	120	123	1.59	15900	0.83	2.9	34	32	13	64	2	9	0.01	7.8	34	0.01
KL16-06	123	126	2.14	21400	0.87	2.8	78	41	16	82	4	10	0.01	7.3	40	0.01
KL16-06	126	129	1.36	13600	0.66	2	116	70	31	70	3	8	0.01	7.5	41	0.01
KL16-06	129	132	1.44	14400	0.57	1.7	122	70	19	50	3	6	0.01	7.8	41	0.01
KL16-06	132	135	1.18	11800	0.91	1.3	77	54	26	121	2	5	0.4	9.8	50	0.01
KL16-06	135	138	1.13	11300	0.93	1.5	44	20	18	76	2	8	0.01	6.0	57	0.01
KL16-06	138	141	0.74	7400	0.95	1.2	34	25	10	78	2	7	0.01	5.7	41	0.01
KL16-06	141	144	0.74	7400	0.75	1	47	20	12	52	2	8	0.01	5.3	41	0.01
KL16-06	144	147	1.32	13200	0.95	2	830	540	88	36	4	9	3.2	17.0	41	0.01
KL16-06	147	150	1.4	14000	0.89	2.1	266	237	73	75	5	10	3.3	14.6	107	0.01
KL16-06	150	153	1.32	13200	1.5	1.7	58	17	21	21	2	7	0.01	9.0	105	0.01
KL16-06	153	156	0.44	4400	0.56	0.9	35	20	15	62	2	7	0.01	12.2	94	0.01
KL16-06	156	159	0.401	4010	1.19	1	46	11	19	50	1	5	0.3	13.0	95	0.01
KL16-06	159	162	0.74	7400	0.92	1.3	87	97	50	44	1	10	7.3	12.3	85	0.01
KL16-06	162	165	1.04	10400	1.08	1.8	630	590	32	38	1	13	5.7	8.8	75	0.01
KL16-06	165	168	1.32	13200	1.29	1.7	160	81	13	78	0.01	13	1.6	5.5	97	0.01
KL16-06	168	169.9	1.77	17700	2.31	2.4	87	53	16	62	1	14	0.9	6.5	95	0.01
KL16-06	169.9	172.5	0.97	9700	1.15	1.5	75	24	10	120	0.01	17	0.5	8.5	110	0.01
KL16-06	172.5	173.9	0.83	8300	0.7	1.2	45	14	8	180	0.01	13	0.5	7.8	125	0.01
KL16-06	173.9	177	0.7	7000	0.69	0.9	52	24	14	75	1	9	1.4	8.1	134	0.01
KL16-06	177	180	0.93	9300	0.8	1.2	46	25	25	72	1	9	0.6	11.3	132	0.01
KL16-06	180	183	0.76	7600	1.1	1.2	101	43	6	53	1	11	0.5	8.0	139	0.01
KL16-06	183	186	1.32	13200	2.29	1.8	56	41	13	62	0.01	12	0.01	8.5	113	0.01
KL16-06	186	189	1.1	11000	1.53	1.5	23	20	11	71	2	10	0.5	8.5	96	0.01
KL16-06	189	192	1.13	11300	1.07	1.7	49	45	52	40	2	9	4.8	8.8	115	0.01
KL16-06	192	195	0.95	9500	1.06	1.3	19	20	7	169	7	7	0.4	5.5	130	0.01
KL16-06	195	198	1.05	10500	0.8	1.5	40	15	11	86	0.01	10	0.8	6.5	86	0.01
KL16-06	198	201	1.94	19400	0.86	2.6	44	20	14	204	1	16	0.6	7.8	86	0.01
KL16-06	201	204	0.99	9900	0.64	1.3	37	17	7	226	0.01	11	0.3	5.8	94	0.01
KL16-06	204	207	1.19	11900	0.46	1.8	52	24	10	260	46	15	0.5	6.5	87	0.01
KL16-06	207	210	1.76	17600	0.79	2.4	126	273	10	212	1	11	0.8	7.8	86	0.01
KL16-06	210	213	1.62	16200	1.21	2.4	49	29	10	204	3	9	0.5	9.5	126	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL16-06	213	216	1.34	13400	2.2	2.1	71	50	16	42	1	16	1	25.5	112	0.01
KL16-06	216	220.1	2.57	25700	2.52	4.1	126	50	17	680	3	16	0.5	13.0	110	0.01
KL16-06	220.1	223.2	0.74	7400	1.2	2.1	132	78	87	61	0.01	17	0.7	19.3	95	0.01
KL16-06	223.2	226.5	0.478	4780	0.47	1.4	88	61	77	45	0.01	16	0.5	4.3	74	0.01
KL16-06	226.5	229.5	0.76	7600	4.84	2.1	144	92	30	134	0.01	15	3.8	21.2	70	0.01
KL16-06	229.5	231.8	1.08	10800	0.46	1.9	277	200	61	32	1	9	1.9	10.8	172	0.01
KL16-06	231.8	234	1.65	16500	1.39	4.9	78	50	25	37	1	16	2.1	12.0	78	0.01
KL16-06	234	236.1	2.3	23000	3.48	4.5	88	40	21	97	3	12	1.3	12.2	94	0.01
KL16-06	236.1	238.5	0.425	4250	0.27	0.8	82	58	60	34	1	3	10.2	8.8	227	0.01
KL16-06	238.5	241.5	1.54	15400	0.26	3.8	1030	360	38	31	6	3	7.2	5.3	206	0.16
KL16-06	241.5	243	0.74	7400	0.1	1.5	119	120	26	6	1	3	4	1.2	149	0.01
KL16-06	243	246	0.8	8000	0.36	1.7	81	104	8	6	0.01	2	2.2	1.5	168	0.01
KL16-06	246	249	0.66	6600	0.19	1.4	81	120	7	8	1	3	1.6	1.5	163	0.01
KL16-06	249	252	0.56	5600	0.28	1.2	68	100	12	10	1	3	1	5.0	187	0.01
KL16-06	252	255	1.07	10700	0.29	2.5	169	165	230	2	1	3	2.2	0.8	255	0.57
KL16-06	255	258	0.86	8600	0.26	4.7	1170	710	13	6	4	2	2.8	2.0	183	0.15
KL16-06	258	261	1.13	11300	0.41	4.1	414	146	33	11	1	3	1.3	3.5	199	0.1
KL16-06	261	264	0.6	6000	0.21	1.1	91	60	27	16	0.01	3	2.1	2.0	121	0.11
KL16-06	264	267	0.76	7600	0.92	1.8	111	110	16	45	0.01	5	1.8	6.3	117	0.01
KL16-06	267	270	0.471	4710	0.19	1.2	164	140	43	57	1	9	1.1	4.0	135	0.01
KL16-06	270	273	0.321	3210	0.3	1.4	66	45	54	37	0.01	25	0.7	14.3	72	0.01
KL16-06	273	276	0.54	5400	0.21	7.7	4180	5400	380	15	10	3	8.9	7.8	243	1.11
KL16-06	276	279	0.87	8700	0.37	3.2	540	375	180	51	0.01	4	12.2	9.8	157	0.18
KL16-06	279	282.5	1.01	10100	0.42	1.8	64	113	13	107	0.01	4	0.7	9.1	249	0.01
KL16-06	282.5	285	1.11	11100	0.5	2.8	68	147	48	154	0.01	8	1.9	6.3	179	0.01
KL16-06	285	288	0.57	5700	0.25	1.6	710	470	33	86	0.01	8	3.2	5.3	143	0.01
KL16-06	288	294	0.58	5800	0.18	1.1	362	256	27	62	0.01	6	4.3	7.4	120	0.01
KL16-06	294	297	0.94	9400	0.31	2.1	328	206	14	186	1	5	1.3	5.0	143	0.01
KL16-06	297	300	0.6	6000	0.26	1	42	40	12	57	1	8	1.4	5.0	163	0.01
KL16-06	300	302.1	0.84	8400	0.29	1.3	31	32	23	116	0.01	4	0.7	2.8	170	0.01
KL16-06	302.1	304.4	0.8	8000	0.26	1.1	85	61	22	147	0.01	5	0.6	5.0	204	0.01
KL16-06	304.4	307.5	0.7	7000	0.2	0.8	87	80	5	173	0.01	5	0.01	4.5	210	0.01
KL16-06	307.5	309.3	0.55	5500	0.15	0.8	750	580	36	37	0.01	5	2.3	6.8	221	0.01
KL16-06	309.3	311.2	0.504	5040	0.14	0.7	131	54	48	54	0.01	4	0.5	5.5	228	0.01
KL16-06	311.2	313.5	0.44	4400	0.11	0.7	95	42	11	63	0.01	4	2.5	6.4	206	0.01
KL16-06	313.5	315.6	0.7	7000	0.16	0.9	180	114	4	61	0.01	5	0.01	9.5	196	0.01
KL16-06	315.6	318.2	0.87	8700	0.37	1.2	32	40	0.01	154	0.01	9	0.01	12.6	211	0.01
KL16-06	318.2	320.7	0.65	6500	0.45	0.8	202	168	23	92	0.01	9	1.2	9.9	200	0.01
KL16-06	320.7	323.8	0.438	4380	0.19	0.6	55	93	4	63	0.01	6	0.01	7.8	210	0.01
KL16-06	323.8	326.9	0.449	4490	0.3	0.8	50	36	3	72	0.01	8	0.01	8.3	237	0.01
KL16-06	326.9	330.2	0.345	3450	0.29	0.7	46	21	4	31	0.01	8	0.01	6.8	224	0.01
KL16-06	330.2	333.2	0.81	8100	0.65	2.2	187	59	59	36	0.01	12	0.6	7.8	218	0.01
KL16-06	333.2	336.2	0.345	3450	0.32	1	34	14	6	89	0.01	18	0.01	11.9	222	0.01
KL16-06	336.2	339.2	0.483	4830	0.45	1.7	38	24	2	46	0.01	10	0.5	8.0	251	0.01
KL16-06	339.2	342.2	0.63	6300	0.48	1.5	44	20	3	61	0.01	11	0.4	7.7	237	0.01
KL16-06	342.2	345.2	0.407	4070	0.19	0.8	256	29	3	70	0.01	10	0.01	5.8	210	0.01
KL16-06	345.2	348.2	0.431	4310	0.21	1	110	61	5	32	0.01	12	0.01	6.3	215	0.01
KL16-06	348.2	351.2	0.325	3250	0.25	0.9	34	16	1	42	0.01	9	0.01	6.5	204	0.01
KL16-06	351.2	354.2	0.304	3040	0.26	0.9	85	20	2	62	0.01	11	0.01	8.0	218	0.01
KL16-06	354.2	357	0.71	7100	0.38	2	890	510	9	93	2	10	0.7	7.0	180	0.1
KL16-06	357	360.2	0.7	7000	0.39	1.1	64	31	4	54	0.01	14	0.01	8.8	204	0.01
KL16-06	360.2	363.2	0.87	8700	0.41	1.8	145	160	12	107	0.01	12	0.3	5.0	214	0.01
KL16-06	363.2	366.2	0.342	3420	0.22	0.8	96	70	3	29	0.01	8	0.01	6.5	237	0.01
KL16-06	366.2	369.2	0.518	5180	0.23	1.1	100	68	10	46	1	10	0.4	7.3	218	0.01
KL16-06	369.2	372.2	0.45	4500	0.18	1.3	500	62	11	62	2	7	0.7	4.8	149	0.01
KL16-06	372.2	374.7	0.276	2760	0.11	0.8	115	89	22	98	0.01	7	1.4	5.5	129	0.01
KL16-06	374.7	377.7	0.271	2710	0.17	0.9	59	47	7	52	0.01	9	0.3	5.3	170	0.01
KL16-06	377.7	380.5	0.438	4380	0.13	1.1	38	29	15	98	0.01	10	0.9	6.7	143	0.01
KL16-06	380.5	387.2	0.54	5400	0.19	1.4	72	57	7	71	0.01	10	0.5	7.3	164	0.01
KL16-06	387.2	390	0.402	4020	0.21	1.3	50	37	21	46	0.01	8	1.4	7.8	174	0.01
KL16-06	390	393.1	0.371	3710	0.13	1.1	32	19	5	40	0.01	9	0.6	9.8	199	0.01
KL16-06	393.1	396.2	0.307	3070	0.09	1.2	32	20	1	126	1	9	0.01	5.3	217	0.01
KL16-06	396.2	399.2	0.39	3900	0.15	1.4	92	51	6	105	1	9	0.01	6.3	195	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL16-06	399.2	402.2	0.24	2400	0.18	1	47	18	8	20	1	7	1.5	6.3	74	0.01
KL16-06	402.2	405.2	0.284	2840	0.33	1.2	110	31	13	66	4	9	0.6	5.3	70	0.01
KL16-06	405.2	409.7	0.82	8200	0.28	1.5	80	38	22	390	2	9	1	9.8	138	0.01
KL16-06	409.7	414.2	0.326	3260	0.2	0.9	90	43	12	250	1	9	0.5	7.3	136	0.01
KL16-06	414.2	416.6	0.85	8500	0.28	1.8	47	23	2	195	4	12	1	8.3	102	0.01
KL16-06	416.6	418.4	0.67	6700	0.17	1.3	37	16	3	96	2	10	0.7	8.5	105	0.01
KL16-06	418.4	420.2	0.55	5500	0.19	1.2	41	20	11	62	2	11	0.4	8.8	103	0.01
KL16-06	420.2	423.2	0.86	8600	0.25	2.1	81	43	39	158	3	11	0.9	9.0	114	0.01
KL16-06	423.2	426.2	1.12	11200	0.24	2.5	57	25	32	363	2	8	2	8.6	61	0.01
KL16-06	426.2	429.2	0.85	8500	0.09	1.5	52	34	42	360	2	8	2.1	5.5	86	0.01
KL16-06	429.2	432.4	1.64	16400	1.24	2.2	100	52	34	595	0.01	15	0.5	11.2	76	0.01
KL16-06	432.4	435.7	1.7	17000	0.58	6.3	380	106	36	330	0.01	14	1.5	9.0	23	0.01
KL16-06	435.7	438.7	0.74	7400	0.26	1.4	84	106	27	146	1	10	0.3	7.9	48	0.01
KL16-06	438.7	441.2	0.441	4410	0.14	1.3	147	49	5	83	1	10	0.01	8.5	54	0.01
KL16-06	441.2	444.2	0.52	5200	0.26	1.2	229	95	7	170	0.01	11	0.3	7.3	52	0.01
KL16-06	444.2	447.2	0.6	6000	0.24	1.1	74	27	7	92	0.01	11	0.2	7.5	60	0.01
KL16-06	447.2	449.9	0.62	6200	0.29	1.1	67	31	2	230	0.01	7	0.01	5.8	61	0.01
KL16-06	449.9	452.5	0.356	3560	0.15	1.3	124	58	8	84	0.01	9	6	6.0	57	0.01
KL16-06	452.5	454.8	0.94	9400	0.3	1.9	44	24	54	167	0.01	18	1.3	9.0	61	0.01
KL16-06	454.8	457.2	0.491	4910	0.11	1	73	65	18	112	0.01	12	1.2	10.0	57	0.01
KL16-06	457.2	460.2	0.81	8100	0.46	1.6	38	23	6	140	0.01	11	0.4	8.3	70	0.01
KL16-06	460.2	462.8	0.82	8200	0.47	1.8	37	26	3	950	0.01	14	0.6	9.3	64	0.01
KL16-06	462.8	465.2	0.92	9200	0.22	1.9	62	80	16	170	0.01	13	2.7	9.0	81	0.01
KL16-06	465.2	468.2	0.57	5700	0.18	1.1	34	19	2	78	0.01	8	0.9	6.3	63	0.01
KL16-06	468.2	471.2	0.64	6400	0.26	1.2	57	31	7	160	0.01	10	0.7	8.5	67	0.01
KL16-06	471.2	474.2	0.65	6500	0.12	1.8	100	66	24	257	0.01	11	1.8	9.0	60	0.01
KL16-06	474.2	477.2	0.54	5400	0.11	1.2	65	30	20	180	0.01	11	1.2	7.5	48	0.01
KL16-06	477.2	480.2	0.76	7600	0.09	2.3	224	164	60	215	0.01	14	3	7.1	258	0.01
KL16-06	480.2	483.2	0.6	6000	0.27	1.3	34	17	2	97	0.01	12	0.4	7.0	116	0.01
KL16-06	483.2	489.2	1.28	12800	0.64	2.6	52	20	2	420	0.01	14	0.6	9.3	342	0.01
KL16-06	489.2	491.7	0.337	3370	0.15	1.1	301	169	4	147	0.01	7	1.1	7.6	59	0.01
KL16-06	491.7	494.1	0.59	5900	0.13	1.7	100	80	36	1450	0.01	8	5.2	7.0	204	0.01
KL16-06	494.1	496.2	0.54	5400	0.13	1.6	87	43	15	259	0.01	7	1.5	10.0	62	0.01
KL16-06	496.2	499.4	0.461	4610	0.16	1.3	48	20	2	330	1	7	0.5	6.8	105	0.01
KL16-06	499.4	505.2	0.84	8400	0.24	2.1	66	48	38	1140	0.01	11	0.7	9.3	53	0.01
KL16-06	505.2	507.7	0.63	6300	0.12	1.2	55	27	40	150	0.01	7	2.1	8.8	45	0.01
KL16-06	507.7	510.8	0.74	7400	0.14	1.1	55	27	34	170	1	8	3.9	7.0	157	0.01
KL16-06	510.8	513.2	0.79	7900	0.32	1.3	45	35	9	668	0.01	13	1.4	6.8	72	0.01
KL16-06	513.2	515.6	0.69	6900	0.26	1.3	103	48	0.01	100	0.01	10	0.7	7.5	178	0.01
KL16-06	515.6	519.1	0.59	5900	0.19	1.8	102	47	24	189	0.01	10	1.6	4.0	63	0.01
KL16-06	519.1	521.2	0.512	5120	0.2	1.4	54	32	3	162	0.01	11	0.6	5.3	199	0.01
KL16-06	521.2	524.4	0.615	6150	0.11	2.5	92	55	140	312	3	8	4	6.9	67	0.01
KL16-06	524.4	528.2	0.51	5100	0.12	1	32	24	37	180	1	7	2	3.9	74	0.01
KL16-06	528.2	531.2	0.44	4400	0.16	0.9	42	25	4	285	0.01	9	0.01	6.0	187	0.01
KL16-06	531.2	534.2	0.7	7000	0.29	1.2	282	57	3	170	1	12	0.8	6.6	59	0.01
KL16-06	534.2	536.1	0.98	9800	0.52	2.3	590	205	1	232	1	18	0.4	6.5	82	0.01
KL16-06	536.1	538.8	1.64	16400	0.68	1.8	116	16	6	38	2	62	0.5	10.8	21	0.01
KL16-06	538.8	541.8	1.06	10600	0.21	0.8	75	18	2	6	3	37	0.3	10.5	13	0.01
KL16-06	541.8	544.3	3.14	31400	1.8	4.1	181	17	8	96	1	104	0.4	9.5	18	0.01
KL16-06	544.3	547.4	0.81	8100	0.68	1.2	235	42	4	34	3	33	0.9	8.0	44	0.01
KL16-06	547.4	549.2	0.65	6500	0.36	1.3	43	16	6	16	0.01	18	0.3	5.5	35	0.01
KL16-06	549.2	551.4	0.75	7500	0.37	2.3	42	14	3	61	0.01	19	0.6	5.5	16	0.01
KL16-06	551.4	554.2	1.31	13100	0.72	3.5	99	17	15	32	0.01	75	0.7	19.0	22	0.01
KL16-06	554.2	557.2	1.29	12900	0.96	4.6	212	25	25	370	1	46	1.1	27.8	23	0.01
KL16-06	557.2	558.3	1.55	15500	1.27	3.7	269	21	14	116	0.01	40	1.8	15.0	22	0.01
KL16-06	558.3	561.2	1.09	10900	0.82	3.1	231	38	13	94	2	30	2.4	12.8	38	0.01
KL16-06	561.2	565.7	2.02	20200	1.14	4	306	36	41	101	0.01	26	0.6	12.5	44	0.01
KL16-06	565.7	568.1	2.99	29900	3.08	9	370	28	18	9	1	44	0.3	13.5	18	0.01
KL16-06	568.1	570.2	3.56	35600	2.78	10.8	292	27	29	19	0.01	31	0.9	7.0	31	0.01
KL16-06	570.2	572.2	2.83	28300	1.7	7.1	57	19	38	36	0.01	72	0.8	17.2	42	0.01
KL16-06	572.2	575.2	2.39	23900	1.52	5.3	337	48	25	28	0.01	22	1.3	12.5	27	0.01
KL16-06	575.2	576.8	0.86	8600	1.16	2.4	313	80	7	2	0.01	48	1.4	7.5	23	0.01
KL16-06	576.8	579.2	0.0186	186	0.01	0.01	64	63	5	28	0.01	2	0.01	0.0	8	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL16-06	579.2	582.2	2.74	27400	1.86	6.5	198	37	20	31	0.01	39	0.8	15.0	16	0.01
KL16-06	582.2	585.9	1.45	14500	1.05	4.5	106	38	15	19	0.01	43	2.3	17.0	44	0.01
KL16-06	585.9	586.7	1.77	17700	1.08	3.8	510	200	8	34	0.01	47	0.8	7.0	36	0.01
KL16-06	586.7	589.7	1.32	13200	0.85	3.5	308	40	10	6	0.01	20	0.5	6.0	32	0.01
KL16-06	589.7	592.7	2.12	21200	1.03	23	14600	9200	58	4	4	20	32	17.7	72	0.23
KL16-06	592.7	595.7	5.24	52400	2.42	16.5	1640	133	62	30	2	51	4.6	14.5	56	0.01
KL16-06	595.7	598.7	1.33	13300	0.75	3.7	235	50	13	107	0.01	26	0.7	17.5	35	0.01
KL16-06	598.7	601.7	0.75	7500	0.38	1.6	109	23	4	19	0.01	17	1.1	7.2	34	0.01
KL16-06	601.7	604.7	0.93	9300	0.44	2.1	83	23	5	36	0.01	11	0.01	9.4	40	0.01
KL16-06	604.7	606.7	0.9	9000	0.36	2.3	107	22	4	189	0.01	33	0.01	11.0	19	0.01
KL16-06	606.7	608.7	1.43	14300	0.47	3.5	226	25	4	26	0.01	46	0.01	22.0	23	0.01
KL16-06	608.7	610.7	0.71	7100	0.4	1	203	27	6	59	0.01	26	0.3	7.3	22	0.01
KL16-06	610.7	613.2	1.85	18500	0.71	4.4	450	25	5	53	0.01	57	0.4	10.2	19	0.01
KL16-06	613.2	615.2	0.61	6100	0.27	1.4	166	26	5	71	0.01	33	0.01	9.6	29	0.01
KL16-06	615.2	618.2	1.68	16800	0.91	5.8	343	21	6	13	1	48	0.6	13.7	34	0.01
KL16-06	618.2	621.2	1.25	12500	0.76	8.2	620	17	8	4	7	45	0.3	11.0	36	0.01
KL16-06	621.2	624.2	1.27	12700	0.55	4.9	540	13	8	2	1	32	0.01	9.4	34	0.01
KL16-06	624.2	627.2	1.03	10300	0.35	5.5	1660	17	7	2	1	76	0.6	10.3	52	0.01
KL16-06	627.2	630.2	1.02	10200	0.51	6.4	1370	37	11	2	4	112	0.4	7.5	38	0.01
KL16-06	630.2	633.2	0.5	5000	0.25	4	780	141	15	6	2	16	0.3	6.0	28	0.01
KL16-06	633.2	636.2	0.077	770	0.06	0.01	149	14	5	5	0.01	0.01	0.01	1.7	17	0.01
KL16-06	636.2	639.2	0.076	760	0.05	0.01	121	13	4	7	0.01	2	0.01	2.6	13	0.01
KL16-06	639.2	642.2	0.177	1770	0.07	1.7	530	16	4	3	0.01	8	0.01	3.5	17	0.01
KL16-06	642.2	645.2	0.33	3300	0.06	2.4	590	13	5	4	0.01	20	0.01	2.2	11	0.01
KL16-06	645.2	648.2	0.6	6000	0.18	2.7	450	13	5	0.01	1	33	0.01	5.0	27	0.01
KL16-06	648.2	651.2	0.37	3700	0.18	2.2	490	13	5	0.01	2	25	0.01	3.0	27	0.01
KL16-06	651.2	654.2	0.041	410	0.01	0.01	244	14	4	0.01	0.01	10	0.01	0.0	10	0.01
KL16-06	654.2	657.2	0.0388	388	0.01	0.01	258	15	6	4	0.01	9	0.01	0.5	10	0.01
KL16-06	657.2	660.2	0.04	400	0.01	0.01	167	12	6	10	0.01	7	0.2	0.7	8	0.01
KL16-06	660.2	663.2	1.35	13500	0.6	7.6	406	21	5	5	14	18	0.01	8.7	27	0.01
KL16-06	663.2	666.2	0.06	600	0.1	0.8	134	15	4	0.01	0.01	0.01	0.01	1.9	10	0.01
KL16-06	666.2	669.2	0.072	720	0.05	0.7	159	14	5	3	0.01	3	0.01	1.5	14	0.01
KL16-06	669.2	672.2	0.053	530	0.02	0.6	219	15	3	0.01	0.01	9	0.01	1.2	16	0.01
KL16-06	672.2	675.2	0.421	4210	0.05	1.8	220	11	5	3	0.01	4	0.01	1.8	15	0.01
KL16-06	675.2	678.2	0.51	5100	0.31	1.1	58	9	5	124	0.01	6	0.01	4.8	22	0.01
KL16-06	678.2	681.2	0.098	980	0.05	0.6	245	10	1	0.01	0.01	8	0.01	0.5	17	0.01
KL16-06	681.2	684.2	0.151	1510	0.08	0.7	198	11	2	2	1	6	0.01	2.3	19	0.01
KL16-06	684.2	687.2	0.0219	219	0.06	0.01	106	8	5	0.01	1	0.01	0.01	0.5	9	0.01
KL16-06	687.2	690.2	0.0317	317	0.03	0.01	161	11	15	3	3	0.01	0.01	0.0	13	0.01
KL16-06	690.2	693.2	0.192	1920	0.25	1	257	17	10	0.01	0.01	3	0.01	2.5	19	0.01
KL16-06	693.2	696.2	0.487	4870	0.13	1.2	250	24	7	21	4	4	0.01	5.4	15	0.01
KL16-06	696.2	699.2	0.91	9100	0.33	6.2	660	13	6	0.01	0.01	27	0.01	9.2	31	0.01
KL16-06	699.2	701.2	1.63	16300	0.51	7.2	397	15	1	0.01	4	42	0.01	13.0	31	0.01
KL16-06	701.2	703.2	1.29	12900	0.69	6.4	219	8	6	0.01	4	26	0.01	9.5	27	0.01
KL16-06	703.2	705.2	0.104	1040	0.06	0.01	234	9	3	0.01	3	6	0.01	1.8	12	0.01
KL16-06	705.2	708.2	0.51	5100	0.21	0.9	69	5	3	15	0.01	7	0.01	4.1	15	0.01
KL16-06	708.2	711.2	0.62	6200	0.39	1	75	11	0.01	78	0.01	11	0.01	6.3	19	0.01
KL16-06	711.2	714.2	0.361	3610	0.17	0.01	46	5	1	0.01	1	5	0.01	3.8	15	0.01
KL16-06	714.2	717.2	0.334	3340	0.15	0.8	63	5	0.01	0.01	0.01	9	0.01	4.5	17	0.01
KL16-06	717.2	719.2	0.14	1400	0.04	0.01	39	6	0.01	29	0.01	3	0.01	2.8	0	0.01
KL16-06	719.2	721.5	0.76	7600	0.26	4.6	352	7	4	0.01	3	14	0.01	5.0	11	0.01
KL16-06	721.5	724.2	0.461	4610	0.22	1.6	580	12	8	0.01	1	12	2.1	6.6	25	0.01
KL16-06	724.2	726.2	0.73	7300	0.52	4	700	10	6	0.01	3	12	0.01	7.6	28	0.01
KL16-06	726.2	729.2	0.64	6400	0.45	1.7	339	10	4	21	1	5	0.01	6.4	29	0.01
KL16-06	729.2	732.2	0.51	5100	0.35	1.1	328	10	5	22	0.01	5	0.01	5.3	19	0.01
KL16-06	732.2	735.2	0.114	1140	0.07	0.01	119	8	7	0.01	0.01	2	0.01	1.3	7	0.01
KL16-06	735.2	738.2	0.268	2680	0.16	0.8	207	8	4	0.01	0.01	3	0.01	3.5	17	0.01
KL16-06	738.2	741.2	0.093	930	0.05	0.01	112	8	6	0.01	0.01	2	0.01	1.1	9	0.01
KL16-06	741.2	744.2	0.09	900	0.03	0.01	121	17	8	0.01	0.01	0.01	0.01	2.6	8	0.01
KL16-06	744.2	747.2	0.99	9900	0.63	3.1	270	10	6	2	2	10	0.01	10.3	36	0.01
KL16-06	747.2	750.2	0.53	5300	0.32	1.6	176	10	6	4	0.01	7	0.01	4.6	44	0.01
KL16-06	750.2	753.2	0.76	7600	0.58	1.4	65	12	5	3	0.01	6	0.01	5.2	36	0.01
KL16-06	753.2	755.4	0.46	4600	0.32	1.3	54	8	1	3	0.01	7	0.01	3.3	29	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL16-06	755.4	757.1	0.46	4600	0.37	1.3	57	8	2	2	0.01	3	0.01	3.3	34	0.01
KL16-06	757.1	759.2	0.071	710	0.02	0.01	35	14	2	10	0.01	2	0.6	1.1	21	0.01
KL16-06	759.2	762.2	0.28	2800	0.17	0.9	40	9	1	7	1	4	0.01	2.5	34	0.01
KL16-06	762.2	765.2	0.062	620	0.01	0.01	26	10	1	18	0.01	2	0.01	0.0	67	0.01
KL16-06	765.2	768.2	0.29	2900	0.06	1.6	128	16	2	15	0.01	4	0.01	2.4	41	0.01
KL16-06	768.2	770.1	0.203	2030	0.07	1.7	196	12	2	4	4	4	0.01	3.2	12	0.01
KL16-06	770.1	771.9	0.51	5100	0.26	2.2	272	35	20	3	3	7	0.4	4.7	36	0.01
KL16-06	771.9	774.1	1.74	17400	0.4	62	7850	900	22300	13	18	26	500	33.8	40	1.77
KL16-06	774.1	777.2	0.067	670	0.01	2.5	500	1060	83	3	3	0.01	6.3	1.8	39	0.01
KL16-06	777.2	779.3	0.36	3600	0.14	2.7	101	470	15	5	4	3	1.2	2.5	10	0.01
KL16-06	779.3	781.7	0.0287	287	0.01	7.7	234	286	76	18	2	3	28	1.5	73	0.01
KL16-06	781.7	783.2	0.0295	295	0.01	0.01	49	20	5	30	0.01	0.01	0.7	0.8	64	0.01
KL16-06	783.2	786.2	0.0115	115	0.01	0.01	68	24	13	10	0.01	2	2.1	0.5	85	0.01
KL16-06	786.2	789.2	0.0119	119	0.01	0.01	21	10	2	6	0.01	2	0.2	0.0	75	0.01
KL16-06	789.2	792.2	0.042	420	0.01	0.01	36	10	2	14	0.01	0.01	0.2	0.6	62	0.01
KL16-06	792.2	795.2	0.0404	404	0.01	0.01	65	22	5	13	0.01	2	0.8	0.8	68	0.01
KL16-06	795.2	798.2	0.0296	296	0.01	0.01	24	14	1	10	0.01	0.01	0.01	0.0	28	0.01
KL16-06	798.2	801.2	0.169	1690	0.27	0.8	19	8	0.01	45	2	0.01	0.01	2.5	14	0.01
KL16-06	801.2	804.2	0.208	2080	0.39	0.01	35	10	3	3	1	0.01	0.01	3.2	10	0.01
KL16-06	804.2	807.2	0.0412	412	0.03	0.01	55	24	2	12	0.01	0.01	0.01	1.1	17	0.01
KL16-06	807.2	810.2	0.45	4500	2.08	0.9	45	13	0.01	6	0.01	7	0.01	4.3	6	0.01
KL16-06	810.2	813.2	0.35	3500	0.21	0.6	44	10	3	4	0.01	10	0.2	3.8	13	0.01
KL16-06	813.2	815.3	0.083	830	0.08	0.01	22	10	0.01	16	0.01	3	0.01	1.0	18	0.01
KL16-06	815.3	817.6	0.37	3700	0.07	0.8	35	12	2	18	1	3	0.3	0.9	17	0.01
KL16-06	817.6	820.2	2.46	24600	3.41	4	98	12	0.01	3	3	28	0.01	9.0	19	0.01
KL16-06	820.2	823.2	1.2	12000	0.81	2.8	30	14	0.01	27	1	5	0.01	6.6	0	0.01
KL16-06	823.2	825.2	1.12	11200	0.4	2.6	97	8	2	4	1	16	0.01	8.2	21	0.01
KL16-06	825.2	828.2	1.7	17000	1.15	6.6	172	11	0.01	5	6	28	0.2	10.0	24	0.01
KL16-06	828.2	831.2	2.32	23200	1.86	10.6	220	12	0.01	2	10	37	0.01	24.7	26	0.01
KL16-06	831.2	834.2	2.54	25400	1.76	8.9	233	10	0.01	0.01	8	34	0.01	31.0	24	0.01
KL16-06	834.2	836.9	0.35	3500	0.18	0.8	60	11	3	66	0.01	9	0.01	3.3	16	0.01
KL16-06	836.9	838.3	1.55	15500	0.81	3.2	179	13	4	29	0.01	34	0.01	7.2	31	0.01
KL16-06	838.3	841.5	0.65	6500	0.3	1.5	56	8	0.01	7	0.01	12	0.01	3.6	13	0.01
KL16-06	841.5	844.7	0.22	2200	0.09	0.7	63	25	0.01	11	1	7	0.6	2.6	17	0.01
KL16-06	844.7	847.7	0.115	1150	0.05	0.5	19	10	0.01	50	0.01	8	0.01	1.2	22	0.01
KL16-06	847.7	850.7	0.08	800	0.05	0.01	17	8	0.01	28	0.01	7	0.01	0.7	28	0.01
KL16-06	850.7	853.1	0.149	1490	0.05	0.01	23	9	0.01	25	0.01	9	0.01	1.5	19	0.01
KL16-06	853.1	855.2	0.128	1280	0.05	0.01	30	12	0.01	21	0.01	9	0.01	1.7	29	0.01
KL16-06	855.2	856.7	0.33	3300	0.12	0.9	89	12	2	36	1	10	0.01	2.6	62	0.01
KL16-06	856.7	858.5	0.27	2700	0.1	0.7	58	11	1	37	1	8	0.01	2.5	55	0.01
KL16-06	858.5	861.2	0.172	1720	0.06	0.5	58	14	0.01	35	0.01	9	0.01	1.9	46	0.01
KL16-06	861.2	864.2	0.121	1210	0.05	0.01	35	8	0.01	22	0.01	6	0.01	1.3	46	0.01
KL16-06	864.2	867.2	0.104	1040	0.03	0.01	32	8	0.01	19	0.01	7	0.01	1.9	48	0.01
KL16-06	867.2	870.2	0.105	1050	0.03	0.01	31	8	0.01	23	0.01	6	0.01	1.8	28	0.01
KL16-06	870.2	873.2	0.099	990	0.03	0.5	43	7	0.01	18	0.01	7	0.01	1.4	48	0.01
KL16-06	873.2	876.2	0.1	1000	0.02	0.01	34	8	0.01	30	0.01	7	0.01	2.3	44	0.01
KL16-06	876.2	879.2	0.088	880	0.02	0.01	27	8	0.01	29	0.01	5	0.01	2.0	48	0.01
KL16-06	879.2	882.2	0.13	1300	0.03	0.5	22	9	1	34	0.01	5	0.01	2.1	36	0.01
KL16-06	882.2	885.2	0.085	850	0.02	0.01	29	9	0.01	30	0.01	5	0.01	1.4	42	0.01
KL16-06	885.2	888.2	0.113	1130	0.04	0.01	30	8	0.01	51	0.01	7	0.01	1.7	47	0.01
KL16-06	888.2	891.2	0.154	1540	0.05	0.01	33	7	0.01	26	0.01	6	0.01	1.6	40	0.01
KL16-06	891.2	894.2	0.134	1340	0.02	0.6	31	7	0.01	69	0.01	5	0.01	2.2	37	0.01
KL16-06	894.2	897.2	0.157	1570	0.06	0.01	27	6	0.01	36	0.01	7	0.01	1.3	52	0.01
KL16-06	897.2	900.2	0.21	2100	0.1	0.7	28	7	0.01	24	0.01	6	0.01	1.7	40	0.01
KL16-06	900.2	903.2	0.074	740	0.02	0.01	19	7	0.01	18	0.01	5	0.01	0.9	41	0.01
KL16-06	903.2	906.2	0.078	780	0.02	0.01	19	6	0.01	15	0.01	5	0.01	0.8	36	0.01
KL16-06	906.2	909.2	0.088	880	0.03	0.01	20	6	0.01	7	0.01	6	0.01	1.2	41	0.01
KL16-06	909.2	912.2	0.073	730	0.02	0.01	19	7	0.01	39	0.01	6	0.01	1.1	38	0.01
KL16-06	912.2	915.2	0.11	1100	0.03	0.01	20	7	0.01	119	0.01	6	0.01	1.3	34	0.01
KL16-06	915.2	918.2	0.128	1280	0.04	0.01	28	7	0.01	20	0.01	8	0.01	1.6	40	0.01
KL16-06	918.2	921.2	0.097	970	0.02	0.01	24	10	0.01	22	0.01	8	0.2	1.2	45	0.01
KL16-06	921.2	924.2	0.146	1460	0.05	0.01	44	12	0.01	14	0.01	8	0.01	2.0	36	0.01
KL16-06	924.2	927.2	0.129	1290	0.04	0.01	43	10	0.01	17	0.01	7	0.01	1.9	66	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL16-06	927.2	930.2	0.061	610	0.03	0.01	27	10	0.01	7	0.01	6	0.01	0.6	60	0.01
KL16-06	930.2	933.2	0.095	950	0.04	0.01	31	12	0.01	7	0.01	5	0.01	1.0	40	0.01
KL16-06	933.2	936.2	0.086	860	0.03	0.01	25	10	0.01	26	0.01	6	0.01	1.4	57	0.01
KL16-06	936.2	939.2	0.08	800	0.03	0.01	20	8	0.01	13	0.01	6	0.01	1.0	65	0.01
KL16-06	939.2	942.2	0.23	2300	0.1	0.01	38	8	0.01	27	0.01	8	0.01	2.3	86	0.01
KL16-06	942.2	944.7	0.129	1290	0.03	0.01	31	10	0.01	28	0.01	8	0.01	2.4	77	0.01
KL16-06	944.7	946.2	1.52	15200	0.61	4.2	218	22	4	8	1	17	0.2	9.5	15	0.01
KL16-06	946.2	948.2	2.11	21100	0.68	4.8	156	12	2	77	0.01	22	0.3	10.2	16	0.01
KL16-06	948.2	951.2	1.84	18400	0.28	5.5	167	11	0.01	59	1	31	0.9	11.0	18	0.01
KL16-06	951.2	954.2	0.86	8600	0.19	3.6	178	18	0.01	22	1	26	1.2	10.8	16	0.01
KL16-06	954.2	957.2	0.77	7700	0.2	3.1	160	17	0.01	8	1	15	0.9	8.0	16	0.01
KL16-06	957.2	959.4	3.01	30100	0.5	8.7	740	16	2	5	2	44	0.3	29.5	17	0.01
KL16-06	959.4	961.5	0.095	950	0.03	0.01	43	13	0.01	17	0.01	4	0.01	1.7	18	0.01
KL16-06	961.5	963.2	0.098	980	0.02	0.01	35	12	0.01	18	0.01	6	0.01	2.0	36	0.01
KL16-06	963.2	966.2	0.064	640	0.01	0.01	22	14	0.01	9	0.01	5	0.01	1.6	28	0.01
KL16-06	966.2	969.2	0.091	910	0.01	0.01	70	24	0.01	26	0.01	9	0.01	2.9	29	0.01
KL16-06	969.2	970.6	0.122	1220	0.02	0.01	70	20	0.01	53	0.01	5	0.01	2.2	36	0.01
KL16-06	970.6	972.2	0.77	7700	0.16	2.6	152	16	4	7	0.01	23	0.01	5.9	18	0.01
KL16-06	972.2	975.2	0.42	4200	0.11	0.9	170	13	0.01	3	0.01	12	0.01	3.4	17	0.01
KL16-06	975.2	978.2	0.42	4200	0.09	1.4	169	10	0.01	4	0.01	14	0.01	7.8	14	0.01
KL16-06	978.2	981.2	0.45	4500	0.07	1.6	148	12	0.01	3	0.01	11	0.4	8.4	9	0.01
KL16-06	981.2	984.2	0.59	5900	0.14	3	188	15	4	12	1	10	0.4	4.2	10	0.01
KL16-06	984.2	987.2	0.8	8000	0.18	3	186	15	0.01	3	0.01	15	0.01	8.5	10	0.01
KL16-06	987.2	990.2	1.24	12400	0.27	4.7	680	13	0.01	23	0.01	24	0.4	11.9	23	0.01
KL16-06	990.2	993.2	0.55	5500	0.11	1.5	300	12	0.01	48	0.01	13	0.2	10.9	16	0.01
KL16-06	993.2	996.2	0.64	6400	0.41	2.2	369	58	26	35	0.01	15	1.4	13.4	14	0.01
KL16-06	996.2	999.2	0.74	7400	0.15	2.8	387	22	9	30	0.01	12	0.2	6.8	14	0.01
KL16-06	999.2	1002.2	0.56	5600	0.13	2.8	372	12	0.01	7	0.01	10	0.01	6.3	15	0.01
KL16-06	1002.2	1005.2	0.55	5500	0.14	2.2	381	11	0.01	15	0.01	10	0.01	9.6	15	0.01
KL16-06	1005.2	1008.2	0.32	3200	0.1	0.8	160	11	2	4	0.01	6	0.01	12.7	14	0.01
KL16-06	1008.2	1011.2	0.78	7800	0.17	2	203	15	0.01	4	0.01	14	0.4	14.0	16	0.01
KL16-06	1011.2	1014.2	0.51	5100	0.1	1.4	175	9	0.01	6	0.01	9	0.01	11.1	11	0.01
KL16-06	1014.2	1017.2	0.59	5900	0.1	1.6	183	10	0.01	18	0.01	5	0.01	9.6	8	0.01
KL16-06	1017.2	1020.2	0.284	2840	0.07	0.9	137	12	0.01	9	0.01	3	0.01	5.8	12	0.01
KL16-06	1020.2	1023.2	0.31	3100	0.16	1	125	11	0.01	17	0.01	8	0.01	5.7	15	0.01
KL16-06	1023.2	1026.2	0.51	5100	0.17	1.3	211	10	0.01	5	0.01	8	0.01	6.7	13	0.01
KL16-06	1026.2	1029.2	0.53	5300	0.19	1.6	238	27	2	10	1	12	0.01	6.0	16	0.01
KL16-06	1029.2	1032.2	0.55	5500	0.21	2	301	15	4	3	1	11	0.01	4.8	17	0.01
KL16-06	1032.2	1035.2	0.59	5900	0.17	1.6	159	0.01	2	53	0.01	13	0.01	4.7	15	0.01
KL16-06	1035.2	1038.2	0.148	1480	0.04	0.01	61	0.01	2	2	0.01	10	0.01	1.5	16	0.01
KL16-06	1038.2	1041.2	0.2	2000	0.06	0.9	41	0.01	1	16	0.01	9	0.01	2.6	11	0.01
KL16-06	1041.2	1044.2	0.35	3500	0.13	1.4	80	18	5	6	2	7	1.6	3.5	9	0.01
KL16-06	1044.2	1047.2	0.075	750	0.01	0.01	23	0.01	2	7	0.01	3	0.01	0.9	12	0.01
KL16-06	1047.2	1049.2	0.131	1310	0.03	0.01	22	0.01	2	5	0.01	2	0.01	1.3	26	0.01
KL16-06	1049.2	1051.2	0.45	4500	0.1	1.4	174	7	3	2	0.01	8	0.01	3.9	26	0.01
KL16-07	0	3	1.02	10200	0.83	1.4	110	54	15	117	0.01	12	0.4	12.5	21	0.01
KL16-07	3	6	0.72	7200	0.59	0.9	132	42	16	195	0.01	12	0.01	9.8	19	0.01
KL16-07	6	9	0.78	7800	0.58	0.5	128	31	15	286	2	14	0.01	16.0	22	0.01
KL16-07	9	12	1.03	10300	0.57	1	173	39	22	46	0.01	14	0.01	16.8	18	0.01
KL16-07	12	15	1.66	16600	0.72	1.8	214	45	33	212	0.01	34	0.01	31.0	24	0.01
KL16-07	15	18	0.63	6300	0.65	0.9	125	17	59	102	0.01	14	0.01	17.8	15	0.01
KL16-07	18	21	0.41	4100	0.85	1.8	850	440	33	840	1	11	1.6	19.8	178	0.01
KL16-07	21	25.5	0.421	4210	0.68	1.8	1700	860	61	271	0.01	10	1.3	18.3	239	0.01
KL16-07	25.5	28.5	0.36	3600	0.53	1.7	720	346	94	71	0.01	10	1.8	25.5	215	0.01
KL16-07	28.5	31.3	0.351	3510	0.86	2	379	92	63	870	0.01	13	0.5	19.8	213	0.01
KL16-07	31.3	33.6	0.177	1770	0.32	0.8	165	19	16	1030	0.01	11	0.2	22.3	188	0.01
KL16-07	33.6	35.7	0.145	1450	0.34	0.5	63	21	15	263	0.01	24	0.2	15.3	98	0.01
KL16-07	35.7	38.5	1.13	11300	2.05	1.6	690	46	20	197	0.01	76	0.6	46.2	97	0.01
KL16-07	38.5	41.5	1.41	14100	1.08	1.7	450	5	10	278	0.01	38	0.01	25.0	23	0.01
KL16-07	41.5	44.5	0.68	6800	0.63	1.1	500	7	10	127	0.01	31	0.01	14.8	26	0.01
KL16-07	44.5	47.5	0.42	4200	0.55	1.2	3200	11	12	39	0.01	25	0.01	19.8	41	0.01
KL16-07	47.5	50.5	0.71	7100	1.08	2.2	3700	45	22	161	0.01	35	0.3	41.3	38	0.01
KL16-07	50.5	52.9	0.491	4910	5.19	1	313	20	36	124	1	26	0.01	16.3	20	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL16-07	52.9	55	2.69	26900	4.35	3.5	6500	5	16	128	2	40	0.2	43.8	21	0.01
KL16-07	55	57.3	3.79	37900	2.33	3.8	2700	9	64	203	2	41	0.01	129.0	47	0.01
KL16-07	57.3	59.5	2.06	20600	3.59	2.4	291	14	14	202	1	51	0.01	72.2	55	0.01
KL16-07	59.5	62.6	4.3	43000	6.52	5.4	235	15	14	85	3	40	0.01	32.5	60	0.01
KL16-07	62.6	65.7	1.43	14300	2.91	2	139	22	6	96	0.01	43	0.01	29.3	51	0.01
KL16-07	65.7	67.7	0.8	8000	0.73	1	77	23	4	15	0.01	8	0.01	16.3	104	0.01
KL16-07	67.7	69.4	3.98	39800	2.25	2.7	171	11	3	67	0.01	50	0.01	38.8	32	0.01
KL16-07	69.4	71.1	2.42	24200	3.83	2.7	96	14	3	28	0.01	41	0.01	66.8	43	0.01
KL16-07	71.1	74.2	1.97	19700	0.76	2	101	34	11	34	0.01	9	0.4	27.0	88	0.01
KL16-07	74.2	76.5	0.512	5120	1.34	1.8	95	61	2	8	0.01	19	0.01	18.5	47	0.01
KL16-07	76.5	79.5	1.49	14900	2.11	1.7	276	29	12	85	0.01	20	0.01	29.5	77	0.01
KL16-07	79.5	82.5	2.59	25900	2.75	2.9	163	28	11	1125	0.01	32	0.01	27.5	82	0.01
KL16-07	82.5	85.5	2.29	22900	1.63	3.8	450	51	33	98	0.01	15	0.6	21.5	90	0.01
KL16-07	85.5	88.2	4.04	40400	4.61	5.1	149	23	46	192	2	24	0.6	18.5	86	0.01
KL16-07	88.2	90.7	1.23	12300	2.04	4.4	246	135	40	151	0.01	5	0.8	5.0	54	0.1
KL16-07	90.7	92.5	0.25	2500	0.36	0.7	29	8	2	115	0.01	10	0.01	2.8	59	0.01
KL16-07	92.5	95.5	1.69	16900	0.85	5.4	46	24	22	77	4	10	0.3	6.0	59	0.01
KL16-07	95.5	98.5	2.93	29300	0.95	9.1	64	48	22	39	5	16	0.3	3.3	56	0.12
KL16-07	98.5	101.5	2.7	27000	0.92	8.9	49	37	26	31	5	11	0.2	5.5	49	0.01
KL16-07	101.5	104.5	2.23	22300	0.78	5.6	70	45	21	30	4	5	0.01	3.7	68	0.01
KL16-07	104.5	107.5	0.78	7800	0.34	2.2	13	13	15	39	7	4	0.01	6.0	61	0.1
KL16-07	107.5	110.5	1.69	16900	0.93	3.8	14	16	36	55	4	6	0.2	2.5	58	0.01
KL16-07	110.5	113.5	1.55	15500	1.12	4	29	14	30	76	3	4	0.6	2.3	55	0.01
KL16-07	113.5	116.5	1.37	13700	1.2	3.5	36	20	3	24	4	6	0.3	7.0	45	0.01
KL16-07	116.5	119.5	1.15	11500	1.29	3.4	42	20	19	30	4	5	0.01	9.1	61	0.01
KL16-07	119.5	122.5	1.27	12700	1.7	3.1	23	16	16	25	5	5	0.01	5.8	45	0.01
KL16-07	122.5	125.5	1.32	13200	1.55	2.7	24	14	20	66	7	6	0.3	4.3	53	0.01
KL16-07	125.5	128.5	0.71	7100	1.12	2	30	16	21	32	7	6	0.01	5.0	48	0.01
KL16-07	128.5	131.5	1.29	12900	1.73	2.8	32	15	33	73	8	7	0.01	5.3	36	0.01
KL16-07	131.5	134	1.06	10600	1.39	2.4	27	10	20	40	5	5	0.01	7.3	37	0.01
KL16-07	134	137	0.85	8500	1.96	1.4	81	37	11	113	2	15	0.3	10.5	47	0.01
KL16-07	137	140	0.76	7600	1.6	1.4	80	46	4	86	1	11	0.8	10.4	73	0.01
KL16-07	140	143	1.17	11700	2.08	2.5	29	26	6	83	2	11	0.8	7.5	59	0.01
KL16-07	143	146	0.96	9600	0.78	3.4	28	20	7	249	3	7	0.6	10.8	32	0.01
KL16-07	146	149	0.51	5100	0.63	1.3	80	158	46	55	2	5	1.5	30.0	37	0.01
KL16-07	149	152	1.24	12400	1.16	2.3	53	24	27	20	5	6	0.01	13.5	48	0.01
KL16-07	152	155	0.74	7400	0.87	1.7	41	22	14	23	6	6	0.01	11.3	54	0.01
KL16-07	155	157	0.69	6900	0.51	1.4	146	28	23	66	3	7	0.01	13.9	22	0.01
KL16-07	157	159	0.462	4620	0.5	1	67	84	31	33	4	5	0.3	12.8	27	0.01
KL16-07	159	162	0.675	6750	0.99	1.7	191	118	20	220	2	6	0.4	16.0	42	0.01
KL16-07	162	165	1.35	13500	1.27	2	308	261	82	81	3	9	1.1	18.0	54	0.01
KL16-07	165	168	1.09	10900	2.04	2.2	74	73	26	72	3	8	0.7	14.7	71	0.01
KL16-07	168	171	0.83	8300	1.04	1.2	62	37	14	68	2	11	1.2	10.5	60	0.01
KL16-07	171	172.9	1.01	10100	1	2	319	141	13	62	2	12	0.6	7.8	70	0.01
KL16-07	172.9	175.3	0.79	7900	0.79	1.6	91	63	10	36	2	8	0.6	5.3	63	0.01
KL16-07	175.3	177.3	1.67	16700	2.22	3.2	35	16	9	204	1	17	0.5	6.0	64	0.01
KL16-07	177.3	180	0.86	8600	2.16	1.7	21	12	5	167	1	12	0.4	7.8	45	0.01
KL16-07	180	183	0.92	9200	2.27	2.7	399	275	36	57	4	5	3.7	11.4	36	0.01
KL16-07	183	186	0.66	6600	1	1.3	58	50	9	47	1	7	0.6	8.5	51	0.01
KL16-07	186	189	0.65	6500	0.89	1.4	41	15	5	87	0.01	13	0.4	8.8	61	0.01
KL16-07	189	192	1	10000	0.92	1.8	100	37	5	132	0.01	16	0.5	5.5	63	0.01
KL16-07	192	195	1.27	12700	0.72	2.6	80	31	8	510	0.01	13	0.5	7.0	70	0.01
KL16-07	195	198	0.98	9800	0.74	2.1	70	40	9	316	0.01	13	0.3	7.8	57	0.01
KL16-07	198	201	0.6	6000	0.45	0.01	46	36	7	203	1	11	0.6	5.5	50	0.01
KL16-07	201	204	0.57	5700	0.37	0.01	32	9	8	146	1	13	0.3	9.5	57	0.01
KL16-07	204	207	0.57	5700	0.62	1.6	62	37	6	189	0.01	11	0.3	7.8	62	0.01
KL16-07	207	210	1.05	10500	1.17	1.3	78	28	13	204	1	17	0.6	9.0	63	0.01
KL16-07	210	213	0.57	5700	0.52	0.7	97	45	10	206	1	16	0.6	8.8	66	0.01
KL16-07	213	216	0.94	9400	1.13	1.4	65	22	8	147	1	11	0.3	5.0	60	0.01
KL16-07	216	219	0.9	9000	1.23	1.4	56	16	7	67	1	17	0.4	7.6	53	0.01
KL16-07	219	222	0.6	6000	0.89	0.7	78	54	9	1040	1	16	0.3	7.3	65	0.01
KL16-07	222	225	1.15	11500	1.32	1.8	45	14	21	362	0.01	16	0.5	10.3	64	0.01
KL16-07	225	228	0.72	7200	0.8	1.2	46	19	17	109	0.01	20	0.3	13.5	70	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL16-07	228	231	0.68	6800	0.45	2	42	16	10	408	0.01	18	0.3	15.5	56	0.01
KL16-07	231	233	0.485	4850	0.47	0.5	39	16	8	412	0.01	14	0.2	12.8	53	0.01
KL16-07	233	237	0.39	3900	0.36	1.3	57	30	20	47	0.01	14	0.01	8.0	52	0.01
KL16-07	237	240	0.74	7400	0.71	1.2	55	15	8	93	0.01	13	0.4	6.5	62	0.01
KL16-07	240	243	0.5	5000	0.52	0.01	51	13	8	50	0.01	10	0.01	5.0	67	0.01
KL16-07	243	246.7	0.322	3220	0.3	0.01	142	17	19	53	0.01	10	0.01	6.3	70	0.01
KL16-07	246.7	249	0.486	4860	0.61	1.2	72	16	4	32	0.01	14	0.01	10.5	65	0.01
KL16-07	249	252	0.327	3270	0.21	0.01	57	17	6	115	0.01	16	0.01	6.1	73	0.01
KL16-07	252	255	0.26	2600	0.45	0.6	60	17	9	14	0.01	7	0.01	4.0	68	0.01
KL16-07	255	258	0.321	3210	0.44	9.3	59	18	9	25	0.01	9	0.01	4.5	62	0.01
KL16-07	258	261.5	0.67	6700	0.63	1.7	87	23	5	42	0.01	15	0.01	12.2	83	0.01
KL16-07	261.5	264.7	0.337	3370	0.25	0.7	129	40	6	17	0.01	7	0.01	4.8	72	0.01
KL16-07	264.7	267	0.73	7300	1.79	1.7	75	26	2	23	2	6	0.01	5.3	118	0.01
KL16-07	267	270	0.78	7800	0.83	2.3	39	37	30	7	1	3	0.5	6.1	107	0.01
KL16-07	270	273	0.513	5130	0.65	0.01	63	23	6	8	1	3	0.01	3.3	96	0.01
KL16-07	273	276	0.422	4220	0.32	0.01	57	26	12	5	1	3	0.01	3.0	114	0.01
KL16-07	276	280.5	0.555	5550	0.42	2.2	101	54	23	3	1	3	0.7	3.7	91	0.01
KL16-07	280.5	283.8	0.55	5500	0.33	1.1	39	17	70	7	1	3	0.9	4.5	119	0.01
KL16-07	283.8	286.8	0.41	4100	0.29	1.3	121	130	370	5	1	2	2.1	2.5	121	0.28
KL16-07	286.8	289.3	0.24	2400	0.48	0.8	378	112	94	5	0.01	3	1	3.0	117	0.26
KL16-07	289.3	292.8	0.36	3600	0.72	0.01	114	40	140	16	0.01	4	0.7	3.8	92	0.01
KL16-07	292.8	295.5	0.479	4790	0.65	0.01	98	32	71	13	0.01	5	0.3	2.8	83	0.01
KL16-07	295.5	298.5	0.56	5600	0.99	2.8	46	17	37	23	1	7	0.8	4.1	98	0.01
KL16-07	298.5	301.5	0.74	7400	0.93	2.1	56	37	20	8	2	6	2.1	7.5	136	0.01
KL16-07	301.5	304.8	0.24	2400	0.15	0.01	61	18	31	12	2	2	1.4	1.0	128	0.01
KL16-07	304.8	307.8	0.464	4640	0.26	0.01	51	14	37	13	1	3	0.2	3.0	127	0.01
KL16-07	307.8	310.8	0.55	5500	0.42	0.01	112	26	28	6	0.01	2	0.2	4.8	140	0.01
KL16-07	310.8	313.8	0.0107	107	0.01	0.01	61	16	1	4	0.01	16	0.01	0.0	17	0.01
KL16-07	313.8	316.8	0.375	3750	0.46	0.01	102	20	11	7	0.01	3	0.01	2.1	129	0.01
KL16-07	316.8	319.7	0.32	3200	0.27	0.01	770	21	140	3	2	2	6.2	1.8	106	0.1
KL16-07	319.7	322.5	0.68	6800	0.4	0.01	61	28	8	14	2	3	0.6	6.6	123	0.01
KL16-07	322.5	325.7	0.435	4350	0.85	1.4	1310	151	270	7	2	4	14.7	4.5	114	0.01
KL16-07	325.7	328.7	0.63	6300	0.55	1.1	92	27	56	15	3	3	0.5	4.6	49	0.01
KL16-07	328.7	331.5	0.511	5110	0.32	1.1	114	66	110	42	1	4	0.6	4.8	90	0.01
KL16-07	331.5	333	0.64	6400	0.3	1	150	44	31	25	0.01	6	0.3	4.8	94	0.01
KL16-07	333	336	0.59	5900	0.52	1.2	117	59	20	27	1	5	0.7	5.0	72	0.01
KL16-07	336	339	0.54	5400	1.27	1.2	43	21	1	6	1	6	0.01	6.0	141	0.01
KL16-07	339	342	0.513	5130	0.8	1	78	28	1	7	1	5	0.01	4.3	154	0.01
KL16-07	342	345	0.58	5800	0.53	1.1	105	45	1	15	0.01	6	0.01	4.5	133	0.01
KL16-07	345	352.2	0.6	6000	0.56	0.7	49	22	2	9	0.01	4	0.01	4.0	106	0.01
KL16-07	352.2	354.7	0.56	5600	0.73	1.7	81	46	8	41	0.01	4	0.3	5.7	120	0.01
KL16-07	354.7	359	0.57	5700	0.8	0.9	55	23	4	22	0.01	5	0.01	6.0	168	0.01
KL16-07	359	362	0.443	4430	0.33	0.6	63	18	2	53	0.01	7	0.01	3.0	185	0.01
KL16-07	362	364.8	0.368	3680	0.4	0.6	49	13	2	30	0.01	6	0.01	4.0	185	0.01
KL16-07	364.8	367.4	0.265	2650	0.29	0.7	77	53	3	10	0.01	6	0.01	2.8	162	0.01
KL16-07	367.4	368.8	0.296	2960	0.34	1	67	26	1	12	0.01	5	0.01	3.8	150	0.01
KL16-07	368.8	372.1	0.75	7500	0.73	1.2	115	25	5	122	0.01	9	1.4	4.8	105	0.01
KL16-07	372.1	375	0.66	6600	0.41	1	112	53	3	53	0.01	11	0.01	4.5	102	0.01
KL16-07	375	378	0.55	5500	0.44	1	115	29	1	298	0.01	12	0.01	5.0	125	0.01
KL16-07	378	381	0.487	4870	0.39	0.9	240	70	4	95	0.01	9	0.01	5.6	100	0.01
KL16-07	381	383	0.339	3390	0.24	0.9	167	38	2	86	0.01	7	0.01	4.5	116	0.01
KL16-07	383	386.8	0.81	8100	0.61	1.5	194	87	1	131	0.01	9	0.3	4.0	118	0.01
KL16-07	386.8	390	0.78	7800	1.09	1.4	105	25	1	14	0.01	6	0.01	5.3	95	0.01
KL16-07	390	393	0.69	6900	0.77	1.3	96	31	2	35	0.01	11	0.7	6.0	161	0.01
KL16-07	393	396	0.7	7000	0.53	1	86	17	4	76	0.01	12	0.01	5.5	129	0.01
KL16-07	396	399	0.72	7200	0.53	1.4	152	60	0.01	74	0.01	13	1.3	6.0	128	0.01
KL16-07	399	402	0.58	5800	0.48	0.9	114	34	0.01	46	0.01	12	0.01	5.3	160	0.01
KL16-07	402	405	0.84	8400	0.51	1.3	50	23	3	27	0.01	10	0.01	5.8	100	0.01
KL16-07	405	408	0.88	8800	0.93	1.2	136	22	30	30	0.01	8	0.01	7.8	120	0.01
KL16-07	408	411	0.445	4450	0.44	0.9	46	16	4	45	0.01	12	0.01	5.3	112	0.01
KL16-07	411	414	0.472	4720	0.36	1.2	61	50	4	291	0.01	10	0.9	3.6	106	0.01
KL16-07	414	417	0.58	5800	0.37	1	84	32	32	68	0.01	9	0.5	5.5	68	0.01
KL16-07	417	420	0.65	6500	0.33	1.1	132	68	13	141	0.01	9	0.01	5.4	72	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL16-07	420	423	0.284	2840	0.16	0.9	168	50	2	38	0.01	8	0.01	3.3	72	0.01
KL16-07	423	426	0.385	3850	0.3	1	125	25	2	47	0.01	11	0.01	6.1	68	0.01
KL16-07	426	428.8	0.49	4900	0.42	0.6	49	26	5	69	1	7	1.4	6.3	128	0.01
KL16-07	428.8	431.9	0.5	5000	0.35	1	68	24	3	77	1	10	0.3	6.3	82	0.01
KL16-07	431.9	435.1	0.76	7600	0.42	1.3	249	30	5	83	1	15	0.8	7.9	98	0.01
KL16-07	435.1	438.1	0.5	5000	0.16	1	154	63	9	115	1	10	1.3	9.2	57	0.01
KL16-07	438.1	441.1	0.44	4400	0.09	0.6	172	57	49	61	1	8	3.2	6.5	84	0.01
KL16-07	441.1	444	0.47	4700	0.14	0.9	158	214	10	45	1	9	1	4.7	121	0.1
KL16-07	444	447.5	0.61	6100	0.3	2.4	63	53	130	44	3	12	7	4.3	31	0.1
KL16-07	447.5	450.5	0.57	5700	0.57	1	148	58	110	85	1	12	2.3	5.8	75	0.1
KL16-07	450.5	453.5	0.75	7500	0.37	1.1	186	93	6	95	0.01	12	0.4	7.6	65	0.01
KL16-07	453.5	456	0.64	6400	0.43	1	359	27	4	71	1	7	0.3	5.5	82	0.01
KL16-07	456	459	0.95	9500	0.46	2.9	112	94	220	107	3	8	3.2	6.0	42	0.01
KL16-07	459	462	0.65	6500	0.53	1.3	83	5	3	166	1	11	0.4	4.8	73	0.01
KL16-07	462	465	0.67	6700	0.67	1.2	156	5	4	80	1	11	0.01	7.0	95	0.01
KL16-07	465	468	0.57	5700	0.19	0.7	56	29	39	33	1	3	0.01	4.9	73	0.01
KL16-07	468	471	0.62	6200	0.47	1.1	42	31	47	45	1	10	0.01	7.0	89	0.01
KL16-07	471	474.5	0.71	7100	0.33	1.2	140	111	150	41	1	8	1.1	4.8	55	0.01
KL16-07	474.5	477.5	0.45	4500	0.25	0.7	149	80	52	84	1	8	0.2	4.5	47	0.01
KL16-07	477.5	480.5	0.43	4300	0.1	1.2	397	286	13	53	1	8	0.7	3.6	54	0.01
KL16-07	480.5	483.7	0.41	4100	0.34	0.01	100	48	2	43	1	8	0.2	4.5	70	0.01
KL16-07	483.7	486.7	0.24	2400	0.17	0.01	79	33	3	37	1	9	0.3	2.0	60	0.01
KL16-07	486.7	489.7	0.45	4500	0.31	0.8	72	23	3	143	1	8	0.01	4.3	71	0.01
KL16-07	489.7	492.7	0.5	5000	0.28	0.8	90	81	2	55	1	8	0.5	4.9	83	0.01
KL16-07	492.7	495.7	0.33	3300	0.17	0.01	85	40	2	35	1	10	0.01	3.5	72	0.01
KL16-07	495.7	498.7	0.27	2700	0.15	0.01	72	31	3	162	0.01	9	0.01	3.5	84	0.01
KL16-07	498.7	501.7	0.33	3300	0.15	0.01	104	36	2	56	0.01	11	0.2	3.8	61	0.01
KL16-07	501.7	504.7	0.34	3400	0.19	0.01	125	58	4	66	0.01	15	0.2	4.8	59	0.01
KL16-07	504.7	507.7	0.45	4500	0.26	0.01	100	27	0.01	32	0.01	13	0.01	5.0	64	0.01
KL16-07	507.7	510.7	0.65	6500	0.25	1	130	58	3	79	1	17	0.3	6.5	67	0.01
KL16-07	510.7	513.7	0.34	3400	0.1	1.8	650	57	8	41	2	13	1	5.8	45	0.01
KL16-07	513.7	516.7	0.27	2700	0.11	3.3	83	87	10	35	5	9	2.3	3.0	34	0.1
KL16-07	516.7	519.7	0.191	1910	0.1	8	3410	6500	250	79	12	8	40	3.1	33	0.64
KL16-07	519.7	521.7	0.31	3100	0.06	3.7	124	88	160	49	8	10	3.4	3.8	24	0.1
KL16-07	521.7	525	0.177	1770	0.05	1.4	2290	96	240	25	6	7	15.3	3.0	39	0.14
KL16-07	525	535.3	0.25	2500	0.06	2.6	278	105	410	28	7	8	42	3.0	43	0.2
KL16-07	535.3	538.3	0.28	2800	0.05	1.3	214	47	110	32	4	10	24	3.0	41	0.01
KL16-07	538.3	541.3	0.27	2700	0.11	0.7	250	160	15	39	1	10	1.4	3.6	75	0.01
KL16-07	541.3	544.5	0.73	7300	0.16	1.4	102	80	14	79	1	9	1.1	6.3	68	0.01
KL16-07	544.5	547.5	0.48	4800	0.12	1.2	148	69	4	70	1	15	0.5	5.0	75	0.01
KL16-07	547.5	550.5	0.42	4200	0.11	1.6	337	128	7	56	2	15	1.2	3.8	85	0.01
KL16-07	550.5	553.5	0.24	2400	0.06	0.6	253	227	3	35	1	10	0.01	4.0	61	0.01
KL16-07	553.5	556.5	0.157	1570	0.03	0.5	520	265	4	33	1	12	0.4	3.8	65	0.01
KL16-07	556.5	559.5	0.27	2700	0.06	0.01	186	130	4	40	0.01	11	0.3	2.8	78	0.01
KL16-07	559.5	563	0.164	1640	0.03	0.01	480	127	12	25	1	9	1.1	2.0	59	0.01
KL16-07	563	566	0.134	1340	0.03	1.2	1520	900	15	55	2	6	1.8	1.7	51	0.01
KL16-07	566	569	0.157	1570	0.03	0.01	430	620	3	34	1	11	0.2	2.0	88	0.01
KL16-07	569	572	0.185	1850	0.03	0.01	500	505	6	30	2	9	0.5	3.6	55	0.01
KL16-07	572	575	0.133	1330	0.05	0.01	266	210	2	25	1	7	0.4	2.4	56	0.01
KL16-07	575	578	0.17	1700	0.05	0.01	403	61	3	63	1	5	0.2	1.5	179	0.01
KL16-07	578	581	0.142	1420	0.04	0.01	203	91	3	96	1	5	0.3	2.0	138	0.01
KL16-07	581	584	0.112	1120	0.05	0.01	181	58	4	45	1	6	0.01	0.5	147	0.01
KL16-07	584	587	0.24	2400	0.1	1.1	204	67	13	25	1	6	0.8	3.0	162	0.01
KL16-07	587	590	0.119	1190	0.03	0.01	71	36	6	21	0.01	13	0.5	1.3	108	0.01
KL16-07	590	593	0.094	940	0.05	0.01	79	40	5	15	0.01	10	0.01	2.0	157	0.01
KL16-07	593	596	0.149	1490	0.07	0.01	116	34	7	18	0.01	8	0.6	2.8	141	0.01
KL16-07	596	599	0.23	2300	0.07	0.01	153	43	1	12	0.01	10	0.3	2.8	200	0.01
KL16-07	599	602	0.095	950	0.08	0.01	142	70	0.01	34	1	8	0.01	0.8	198	0.01
KL16-07	602	605	0.192	1920	0.11	0.01	82	19	3	24	1	8	0.2	0.8	173	0.01
KL16-07	605	608	0.31	3100	0.08	1.6	1100	93	18	20	1	10	7.9	3.6	245	0.1
KL16-07	608	611	0.23	2300	0.06	1	351	188	1	18	1	6	0.5	2.7	231	0.01
KL16-07	611	614	0.31	3100	0.16	1.2	108	21	3	18	1	8	0.01	1.5	217	0.01
KL16-07	614	617	0.49	4900	0.07	3.5	142	126	78	23	2	6	13	1.8	280	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL16-07	617	620	0.45	4500	0.27	1.6	164	28	44	20	1	7	6.4	4.3	212	0.01
KL16-07	620	623	0.5	5000	0.22	1.4	119	17	2	23	0.01	11	0.9	4.8	309	0.01
KL16-07	623	626	0.33	3300	0.14	1.3	203	31	8	15	1	9	1.3	2.8	150	0.01
KL16-07	626	629	0.35	3500	0.06	1.6	730	89	47	22	1	6	1.7	2.8	78	0.01
KL16-07	629	632	0.32	3200	0.06	3	590	113	21	15	2	6	1.7	3.1	89	0.1
KL16-07	632	635	0.304	3040	0.06	0.01	189	40	4	28	0.01	8	0.4	4.9	54	0.01
KL16-07	635	638	0.438	4380	0.11	0.8	29	9	8	12	1	5	0.01	2.9	69	0.01
KL16-07	638	641	0.228	2280	0.12	0.01	54	15	1	26	0.01	14	0.01	3.1	61	0.01
KL16-07	641	644	0.157	1570	0.03	0.01	46	19	0.01	24	0.01	5	0.01	1.0	93	0.01
KL16-07	644	647	0.14	1400	0.04	0.01	44	17	0.01	32	0.01	7	0.01	2.3	67	0.01
KL16-07	647	650	0.119	1190	0.02	0.01	312	130	2	34	0.01	6	0.5	1.3	73	0.01
KL16-07	650	652.3	0.114	1140	0.02	0.01	30	12	0.01	25	0.01	7	0.3	1.4	96	0.01
KL16-07	652.3	654	0.121	1210	0.04	0.01	101	40	2	29	0.01	8	0.3	2.0	58	0.01
KL16-07	654	656	0.154	1540	0.05	0.01	64	30	4	21	0.01	8	1.1	1.8	77	0.01
KL16-07	656	659	0.233	2330	0.07	0.01	73	30	3	60	0.01	8	0.7	3.8	57	0.01
KL16-07	659	662	0.268	2680	0.11	1.5	140	30	26	19	1	4	1.9	1.0	50	0.1
KL16-07	662	665	0.342	3420	0.08	0.8	311	69	18	40	1	8	1.1	3.2	59	0.01
KL16-07	665	668	0.229	2290	0.18	0.8	266	71	1	27	0.01	9	0.01	4.6	96	0.01
KL16-07	668	671	0.229	2290	0.04	1.3	540	175	56	40	1	9	5.9	2.5	59	0.1
KL16-07	671	674	0.14	1400	0.03	1.7	1610	154	25	33	1	6	1.3	0.8	58	0.01
KL16-07	674	677	0.279	2790	0.07	3.2	3060	180	16	30	3	8	0.8	2.0	51	0.1
KL16-07	677	678.4	0.19	1900	0.05	1.6	410	126	3	20	1	12	0.3	1.9	99	0.01
KL16-08	0	3	0.93	9300	0.76	1.1	74	50	9	690	0.01	13	0.7	10.0	23	0.01
KL16-08	3	6	0.84	8400	1.34	1	48	34	12	285	0.01	13	0.2	10.3	20	0.01
KL16-08	6	9	0.85	8500	0.77	1.2	63	30	20	314	0.01	14	0.6	14.5	26	0.01
KL16-08	9	12	1.05	10500	1.24	0.7	56	23	25	46	1	15	0.01	17.5	13	0.01
KL16-08	12	15	1.11	11100	0.95	1.2	84	31	17	540	0.01	17	0.01	14.5	17	0.01
KL16-08	15	18	1.06	10600	1.89	1.2	80	24	14	84	0.01	21	0.01	22.5	13	0.01
KL16-08	18	21	0.74	7400	0.97	0.9	157	34	17	870	0.01	12	0.3	13.0	36	0.01
KL16-08	21	24	0.55	5500	2.21	1.3	191	16	25	1340	0.01	12	0.8	23.5	79	0.01
KL16-08	24	27	0.72	7200	1.07	3.7	590	1140	37	530	0.01	11	1.2	38.0	56	0.01
KL16-08	27	30	0.36	3600	0.95	1.1	141	40	20	456	0.01	10	1.5	20.5	58	0.01
KL16-08	30	33	0.39	3900	0.74	1.3	2010	1960	26	1890	0.01	12	0.7	25.4	87	0.17
KL16-08	33	35	0.33	3300	0.52	0.01	402	214	8	930	0.01	18	0.7	14.7	115	0.01
KL16-08	35	37.5	0.65	6500	0.7	0.9	382	30	12	181	0.01	22	0.2	11.8	24	0.01
KL16-08	37.5	40.5	1.16	11600	0.89	1.4	2980	15	9	171	0.01	57	0.01	20.0	18	0.01
KL16-08	40.5	43.5	0.51	5100	0.47	0.01	148	15	8	137	0.01	27	0.01	9.5	17	0.01
KL16-08	43.5	46.5	0.43	4300	0.4	0.01	109	16	9	82	0.01	23	0.01	9.8	32	0.01
KL16-08	46.5	49.5	0.27	2700	0.33	0.01	163	16	12	42	0.01	18	0.01	5.3	26	0.01
KL16-08	49.5	51	0.34	3400	0.32	0.01	175	28	9	37	0.01	15	0.01	5.9	28	0.01
KL16-08	51	54	0.78	7800	0.74	0.6	268	24	6	27	0.01	22	0.5	7.8	22	0.01
KL16-08	54	57	0.51	5100	0.81	0.6	130	36	8	11	0.01	13	0.3	9.3	37	0.01
KL16-08	57	60	1.4	14000	1.89	1.7	132	19	12	86	0.01	33	0.01	23.3	28	0.01
KL16-08	60	63	0.71	7100	0.6	0.6	157	10	6	79	0.01	26	0.01	12.0	19	0.01
KL16-08	63	66	0.5	5000	0.65	0.01	66	12	4	54	0.01	20	0.01	12.5	23	0.01
KL16-08	66	68.2	0.52	5200	0.63	0.6	82	12	13	273	1	17	0.01	11.0	26	0.01
KL16-08	68.2	70.2	0.67	6700	0.59	0.9	65	11	13	77	0.01	46	0.01	46.0	24	0.01
KL16-08	70.2	73.2	2.03	20300	2.5	2.6	108	24	19	135	0.01	28	0.01	22.5	19	0.01
KL16-08	73.2	75.1	1.04	10400	1.41	2	132	14	10	131	0.01	34	0.01	24.5	38	0.01
KL16-08	75.1	77.4	4.1	41000	3.06	4.8	322	30	2	96	0.01	58	0.01	15.0	32	0.01
KL16-08	77.4	78.9	1.74	17400	2.07	2	109	19	14	220	0.01	31	0.01	20.8	41	0.01
KL16-08	78.9	81.7	1.73	17300	1.89	2.6	123	20	8	130	0.01	42	0.01	27.5	69	0.01
KL16-08	81.7	84	1.75	17500	2.28	1.5	84	16	0.01	23	0.01	24	0.01	15.5	39	0.01
KL16-08	84	87	2.45	24500	2.81	2.6	92	16	4	57	1	24	0.01	13.8	40	0.01
KL16-08	87	90	3.89	38900	2.3	3.2	90	14	0.01	169	1	30	0.2	23.1	46	0.01
KL16-08	90	93	2.69	26900	2.89	2.8	185	16	2	109	2	35	0.01	17.5	70	0.01
KL16-08	93	96	1.78	17800	3.12	2	58	20	6	150	0.01	24	0.01	14.5	81	0.01
KL16-08	96	99	1.3	13000	1.65	1.4	114	27	4	399	0.01	27	0.4	13.0	87	0.01
KL16-08	99	102	3.02	30200	4.05	3.1	109	34	5	48	1	30	0.9	24.4	75	0.01
KL16-08	102	105	2.74	27400	2.89	3.5	135	26	6	94	0.01	24	0.4	16.3	93	0.01
KL16-08	105	108	0.37	3700	0.59	2.2	810	180	180	13	0.01	3	7.3	5.1	100	0.18
KL16-08	108	111	0.89	8900	1.81	3.7	367	165	470	293	1	4	12.3	8.4	66	0.12
KL16-08	111	114	0.32	3200	0.66	0.6	51	35	35	221	0.01	3	0.5	5.0	115	0.1

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL16-08	114	117	0.37		3700	0.68	0.01	196	123	19	282	0.01	3	1.1	6.5	82	0.01
KL16-08	117	120	1.65		16500	2.48	2	76	53	21	91	2	6	0.7	25.5	105	0.01
KL16-08	120	123	1.51		15100	1.98	2.5	57	46	20	61	3	8	1.1	22.0	117	0.01
KL16-08	123	126	1.68		16800	2.68	3.7	96	72	16	52	3	6	0.5	24.5	77	0.14
KL16-08	126	129	2.45		24500	1.09	5.3	298	282	31	55	9	5	1.3	27.6	111	0.1
KL16-08	129	132	1.1		11000	0.83	1.3	80	82	30	33	4	4	0.3	14.0	47	0.01
KL16-08	132	135	0.83		8300	0.73	1.1	285	316	65	25	2	4	2.1	8.1	42	0.1
KL16-08	135	137.5	0.72		7200	0.98	0.01	113	60	16	141	1	5	0.6	9.8	47	0.01
KL16-08	137.5	140.5	0.68		6800	0.82	0.01	38	46	22	41	1	4	0.4	11.8	43	0.01
KL16-08	140.5	143.5	0.94		9400	1.04	1.5	69	64	9	58	2	7	0.01	9.5	57	0.01
KL16-08	143.5	146.9	0.89		8900	0.71	0.7	349	372	15	47	2	6	0.5	9.9	103	0.01
KL16-08	146.9	150	1.07		10700	1.36	2	103	225	73	28	3	7	2.3	27.3	87	0.01
KL16-08	150	153	1.2		12000	1.13	0.01	39	36	22	48	0.01	6	1.4	15.5	93	0.01
KL16-08	153	156	0.72		7200	1.14	0.01	138	59	34	39	1	7	1.2	14.5	75	0.01
KL16-08	156	159	1.3		13000	1.16	3	230	159	68	28	1	7	2.6	18.0	82	0.1
KL16-08	159	162	0.63		6300	0.83	0.01	194	140	22	57	0.01	6	0.8	12.3	75	0.01
KL16-08	162	165	1.21		12100	3.44	0.01	37	31	3	38	1	10	0.01	12.7	80	0.01
KL16-08	165	167.3	1.19		11900	1.18	0.8	40	36	6	19	1	9	0.01	15.5	67	0.01
KL16-08	167.3	169.5	0.91		9100	1.7	0.01	39	41	8	44	0.01	10	0.01	12.0	47	0.01
KL16-08	169.5	172.5	0.97		9700	1.21	0.01	148	130	6	25	1	9	0.3	10.3	60	0.01
KL16-08	172.5	175.6	1.54		15400	1.25	1.3	295	191	9	33	0.01	8	0.4	8.0	60	0.01
KL16-08	175.6	178.7	1.16		11600	3.06	1.5	51	34	11	95	1	10	0.5	16.0	63	0.01
KL16-08	178.7	181.5	0.81		8100	1.36	0.01	33	13	10	86	0.01	8	0.01	8.1	73	0.01
KL16-08	181.5	183.9	0.0122		122	0.01	0.01	69	19	2	2	0.01	13	0.01	0.0	20	0.01
KL16-08	183.9	186	0.67		6700	0.81	0.01	80	36	4	66	0.01	11	0.01	8.3	60	0.01
KL16-08	186	189	0.54		5400	0.4	1.1	126	63	8	76	0.01	10	0.5	6.3	102	0.01
KL16-08	189	192	0.82		8200	0.82	0.01	43	9	5	104	0.01	11	0.2	8.3	100	0.01
KL16-08	192	195	1.07		10700	0.72	0.01	26	5	5	251	0.01	16	0.01	15.0	108	0.01
KL16-08	195	198	0.68		6800	0.92	0.01	36	22	6	43	3	8	0.01	16.3	128	0.01
KL16-08	198	201	1.33		13300	1.67	1.7	38	15	6	62	1	12	0.01	19.0	124	0.01
KL16-08	201	204	0.85		8500	0.79	0.01	37	11	8	103	0.01	13	0.01	8.8	118	0.01
KL16-08	204	207	1.02		10200	0.73	0.01	48	16	8	218	0.01	20	0.5	11.0	130	0.01
KL16-08	207	210	1.01		10100	0.87	1.1	51	24	15	189	0.01	11	1.3	11.5	105	0.01
KL16-08	210	213	0.49		4900	0.52	0.01	46	20	11	166	0.01	10	0.01	8.3	100	0.01
KL16-08	213	216	0.69		6900	0.55	0.01	107	35	9	199	0.01	12	0.01	8.3	105	0.01
KL16-08	216	219	0.65		6500	0.63	0.01	51	13	4	115	0.01	12	0.01	7.8	75	0.01
KL16-08	219	222	0.61		6100	0.46	0.01	53	18	4	74	0.01	14	0.6	7.3	70	0.01
KL16-08	222	225	0.72		7200	0.92	0.01	55	19	3	160	0.01	10	0.01	7.5	100	0.01
KL16-08	225	228	0.53		5300	0.4	0.01	51	16	2	378	0.01	18	0.01	7.5	70	0.01
KL16-08	228	231	0.42		4200	0.26	0.01	58	14	3	165	0.01	14	0.01	8.0	60	0.01
KL16-08	231	234	0.78		7800	0.52	0.01	71	28	0.01	81	0.01	17	0.01	9.5	78	0.01
KL16-08	234	237	0.81		8100	0.95	0.01	56	15	0.01	75	0.01	13	0.01	7.8	90	0.01
KL16-08	237	240	0.69		6900	0.58	0.8	53	8	0.01	245	0.01	11	0.01	6.5	66	0.01
KL16-08	240	243	0.6		6000	0.54	0.6	57	65	3	127	0.01	16	0.01	7.5	87	0.01
KL16-08	243	246	0.55		5500	0.4	0.01	43	13	1	105	0.01	10	0.01	5.3	84	0.01
KL16-08	246	249	0.62		6200	0.46	0.01	60	18	3	101	0.01	19	0.3	7.0	86	0.01
KL16-08	249	252	0.6		6000	0.48	0.01	68	19	4	111	0.01	17	0.01	6.3	79	0.01
KL16-08	252	255	0.57		5700	0.51	1.3	75	29	7	189	0.01	21	0.9	7.3	93	0.01
KL16-08	255	258	0.68		6800	0.57	0.5	224	164	10	33	0.01	26	0.3	11.5	101	0.01
KL16-08	258	260	0.81		8100	0.51	0.8	154	113	5	176	0.01	20	0.3	9.4	100	0.01
KL16-08	260	262.5	0.9		9000	0.65	1.3	103	43	2	96	0.01	16	0.01	9.0	124	0.01
KL16-08	262.5	265.3	0.68		6800	0.38	0.6	56	18	3	64	0.01	15	0.3	7.5	84	0.01
KL16-08	265.3	268.3	0.75		7500	0.49	1.2	70	16	2	89	0.01	18	0.01	10.8	100	0.01
KL16-08	268.3	271.5	0.73		7300	0.4	0.5	52	12	2	62	0.01	17	0.2	9.8	107	0.01
KL16-08	271.5	274.5	0.51		5100	0.36	0.01	44	7	3	36	0.01	10	0.01	6.3	94	0.01
KL16-08	274.5	277.5	0.29		2900	0.17	0.01	29	9	3	38	0.01	9	0.01	4.1	82	0.01
KL16-08	277.5	280.5	0.5		5000	0.41	1	36	9	0.01	34	0.01	11	0.4	7.4	51	0.01
KL16-08	280.5	284.5	0.289		2890	0.27	0.6	30	12	1	32	0.01	8	0.01	5.2	52	0.01
KL16-08	284.5	287.7	0.361		3610	0.31	0.7	38	10	4	36	0.01	12	0.01	7.0	53	0.01
KL16-08	287.7	290.7	0.64		6400	0.53	1.3	43	8	5	60	0.01	16	0.2	6.5	60	0.01
KL16-08	290.7	292.5	1.59		15900	1.37	2.3	90	17	14	169	1	16	0.4	11.5	63	0.01
KL16-08	292.5	295.5	0.276		2760	0.23	0.8	46	18	15	34	0.01	8	0.5	7.9	71	0.01
KL16-08	295.5	298.5	0.432		4320	0.49	1.2	72	26	8	37	0.01	12	0.2	6.8	65	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL16-08	298.5	301.5	0.181	1810	0.25	0.8	52	21	0.01	24	0.01	8	0.01	2.6	66	0.01
KL16-08	301.5	304.5	0.41	4100	0.34	1.2	65	18	5	54	0.01	12	0.2	7.5	57	0.01
KL16-08	304.5	307.5	0.68	6800	0.84	1.3	77	25	6	48	0.01	13	0.01	7.3	57	0.01
KL16-08	307.5	310.5	0.62	6200	0.68	1.7	94	34	7	25	0.01	16	0.3	9.8	58	0.01
KL16-08	310.5	313.5	1.52	15200	1.63	3	520	212	110	142	2	10	3.2	12.8	51	0.01
KL16-08	313.5	316.5	0.304	3040	0.42	0.9	40	28	210	14	1	0.01	2	3.8	31	0.01
KL16-08	316.5	319.5	0.434	4340	0.67	0.9	49	34	32	7	1	0.01	2.4	3.3	62	0.01
KL16-08	319.5	322.5	0.331	3310	0.76	1	48	27	5	19	2	2	1.2	5.1	50	0.01
KL16-08	322.5	325.5	0.302	3020	1.22	0.8	45	17	0.01	14	1	3	0.5	0.0	42	0.01
KL16-08	325.5	328.5	0.193	1930	0.63	0.9	34	17	0.01	16	0.01	0.01	0.4	0.7	56	0.01
KL16-08	328.5	331.5	0.452	4520	0.44	1.3	36	17	5	20	0.01	0.01	0.7	2.8	41	0.01
KL16-08	331.5	334.5	0.54	5400	0.38	2.1	360	900	51	38	1	4	17.5	1.0	39	0.14
KL16-08	334.5	337.5	0.635	6350	0.41	2.1	55	33	36	25	2	3	1.9	6.3	52	0.01
KL16-08	337.5	340.5	0.404	4040	0.29	1.7	56	25	47	13	0.01	2	1.9	2.8	46	0.01
KL16-08	340.5	343.5	0.224	2240	0.2	0.9	37	15	44	6	0.01	2	0.8	1.0	42	0.01
KL16-08	343.5	346.5	0.58	5800	0.8	1.4	35	16	24	18	0.01	2	0.9	4.7	59	0.01
KL16-08	346.5	349.5	0.394	3940	0.38	1.3	205	20	5	34	0.01	8	0.6	1.4	63	0.01
KL16-08	349.5	352.5	0.261	2610	0.23	1	73	22	7	33	0.01	10	0.5	2.8	68	0.01
KL16-08	352.5	355.5	0.391	3910	0.35	2.6	132	65	49	44	0.01	10	19.6	4.4	107	0.01
KL16-08	355.5	358.5	0.412	4120	0.58	1.1	65	21	8	36	1	8	0.3	1.0	105	0.01
KL16-08	358.5	361.5	0.353	3530	0.37	1.2	81	20	13	21	0.01	4	0.6	0.5	43	0.01
KL16-08	361.5	364.5	0.431	4310	0.48	2.2	690	40	170	10	0.01	3	0.8	2.8	43	0.01
KL16-08	364.5	367.5	0.4	4000	0.13	1.9	168	75	160	10	0.01	3	3.7	4.2	52	0.01
KL16-08	367.5	370.5	0.384	3840	0.22	1.6	118	40	39	15	0.01	7	0.6	1.3	52	0.01
KL16-08	370.5	373.5	0.281	2810	0.17	4.7	4290	3630	19	14	0.01	3	2	3.0	55	0.01
KL16-08	373.5	376.5	0.344	3440	0.36	1.5	620	388	12	17	0.01	6	0.4	2.3	61	0.01
KL16-08	376.5	379.5	0.481	4810	0.53	1.7	295	36	46	13	0.01	4	4.4	2.0	70	0.01
KL16-08	379.5	380.3	0.311	3110	0.29	2	181	41	47	4	1	4	15.1	0.5	86	0.01
KL16-09	0	3	0.58	5800	0.46	1	106	30	9	2300	0.01	10	0.7	7.8	24	0.01
KL16-09	3	5.6	0.84	8400	0.77	1.3	96	26	8	232	0.01	12	0.01	5.8	18	0.01
KL16-09	5.6	8.6	0.71	7100	0.61	0.8	62	34	9	142	0.01	12	0.3	8.5	24	0.01
KL16-09	8.6	11.6	0.449	4490	0.85	0.6	56	29	8	331	0.01	8	0.3	5.5	48	0.01
KL16-09	11.6	14.6	0.78	7800	0.76	1.3	39	23	12	265	0.01	11	0.2	6.8	24	0.01
KL16-09	14.6	17.6	0.61	6100	0.66	1	149	24	18	277	1	10	0.5	4.7	24	0.01
KL16-09	17.6	20.6	0.97	9700	1	0.7	66	16	12	360	1	14	0.2	9.3	17	0.01
KL16-09	20.6	23.6	0.89	8900	0.86	1	47	9	7	229	0.01	10	0.01	10.0	14	0.01
KL16-09	23.6	26.6	0.82	8200	1.54	1.3	103	14	27	340	0.01	12	0.5	10.7	41	0.01
KL16-09	26.6	29.6	0.291	2910	1.06	0.5	98	15	15	300	0.01	11	0.8	6.0	86	0.01
KL16-09	29.6	32.6	0.59	5900	1.07	0.8	110	26	9	146	0.01	13	0.6	10.0	50	0.01
KL16-09	32.6	35.6	0.464	4640	0.94	0.9	160	32	10	227	0.01	13	1.2	6.8	60	0.01
KL16-09	35.6	38.6	0.468	4680	0.73	1	170	28	11	345	0.01	15	0.8	9.7	64	0.01
KL16-09	38.6	41.6	0.409	4090	1.36	1.1	820	29	22	238	0.01	13	0.6	12.8	70	0.01
KL16-09	41.6	44.6	0.339	3390	1.47	0.01	110	26	24	287	2	10	0.3	12.0	100	0.01
KL16-09	44.6	47.6	0.435	4350	0.85	1.5	600	680	18	223	0.01	12	0.7	13.4	247	0.01
KL16-09	47.6	50.1	0.242	2420	0.83	0.01	250	56	69	870	0.01	16	2.9	19.0	131	0.01
KL16-09	50.1	53.3	0.356	3560	0.54	1	380	780	16	434	0.01	16	0.5	30.2	160	0.01
KL16-09	53.3	56.5	0.471	4710	0.32	0.6	100	200	7	368	0.01	12	1	12.7	43	0.01
KL16-09	56.5	59.6	0.324	3240	0.22	0.01	67	25	8	460	0.01	18	0.3	6.8	26	0.01
KL16-09	59.6	61.1	0.34	3400	0.76	0.6	120	11	19	760	0.01	15	0.2	5.5	27	0.01
KL16-09	61.1	64.1	1.02	10200	1.05	1.1	70	6	7	149	0.01	22	0.01	7.3	24	0.01
KL16-09	64.1	67.1	1.22	12200	1.06	1.5	82	10	5	650	0.01	25	0.01	12.5	16	0.01
KL16-09	67.1	70.1	1.41	14100	0.68	1.5	270	12	3	510	2	35	0.01	9.3	16	0.01
KL16-09	70.1	73.1	1.09	10900	0.97	0.9	76	6	2	13	0.01	36	0.01	8.0	16	0.01
KL16-09	73.1	76.1	1.12	11200	0.94	1.6	167	18	4	32	0.01	24	0.01	11.7	16	0.01
KL16-09	76.1	79.1	0.74	7400	0.8	1.4	207	9	1	35	0.01	33	0.01	9.0	18	0.01
KL16-09	79.1	82.1	0.78	7800	4.2	1.9	20600	46	33	442	58	55	0.2	12.0	10	0.01
KL16-09	82.1	85.1	1.36	13600	1.75	2	5000	23	22	630	4	61	0.01	15.2	17	0.01
KL16-09	85.1	88.1	1.31	13100	1.44	1.6	372	16	55	1920	3	42	0.01	8.5	24	0.01
KL16-09	88.1	91.1	0.59	5900	0.54	0.8	107	8	5	78	0.01	22	0.01	11.5	26	0.01
KL16-09	91.1	94.1	1.84	18400	2.25	5.5	64	14	1	41	3	15	0.01	8.5	17	0.01
KL16-09	94.1	97.1	0.93	9300	0.92	1.5	86	10	1	452	3	20	0.01	11.0	20	0.01
KL16-09	97.1	100.1	1.78	17800	2.79	1.7	51	13	1	147	0.01	14	0.01	10.5	25	0.01
KL16-09	100.1	102.2	1.75	17500	0.88	3.2	55	14	0.01	6	3	16	0.01	11.7	20	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL16-09	102.2	104.6	1.7	17000	2.82	3.9	90	15	1	4	4	17	0.01	8.0	17	0.01
KL16-09	104.6	107.6	1.38	13800	1.28	1.3	1050	7	13	19	1	42	0.01	9.8	23	0.01
KL16-09	107.6	109.9	0.365	3650	0.51	0.01	74	6	20	453	0.01	21	0.01	6.7	19	0.01
KL16-09	109.9	111.9	1.04	10400	1.67	1.2	43	5	8	198	2	12	0.2	6.1	20	0.01
KL16-09	111.9	115.1	3.4	34000	5.26	3.7	72	18	0.01	170	0.01	26	0.01	13.0	23	0.01
KL16-09	115.1	118.1	4.01	40100	4.72	4	80	17	1	20	1	21	0.01	29.0	17	0.01
KL16-09	118.1	121.1	2.21	22100	2.41	2.1	87	16	1	13	0.01	20	0.01	23.0	25	0.01
KL16-09	121.1	124.1	1.39	13900	1.55	1.1	89	10	0.01	85	0.01	22	0.01	18.0	15	0.01
KL16-09	124.1	127.1	2.68	26800	3.61	2.5	80	12	0.01	4	0.01	20	0.01	18.0	10	0.01
KL16-09	127.1	130.1	2.12	21200	2.87	2.8	76	19	0.01	5	5	20	0.01	17.0	13	0.01
KL16-09	130.1	133.1	3.31	33100	7.23	4.2	84	14	0.01	8	12	21	0.01	17.0	20	0.01
KL16-09	133.1	136.1	1.6	16000	5.71	2.8	83	14	0.01	24	9	20	0.01	16.0	17	0.01
KL16-09	136.1	139.1	2.68	26800	3.4	4.7	70	18	1	415	5	20	0.01	20.0	26	0.01
KL16-09	139.1	142.1	1.47	14700	2.04	1.4	89	12	0.01	86	1	20	0.7	12.5	24	0.01
KL16-09	142.1	145.1	1.81	18100	1.57	2.3	63	15	0.01	77	1	23	0.01	17.0	36	0.01
KL16-09	145.1	148.1	2.18	21800	1.42	2.1	40	10	1	38	0.01	22	0.01	21.0	41	0.01
KL16-09	148.1	151.1	1.05	10500	0.69	1.2	54	13	0.01	195	0.01	17	0.01	10.7	49	0.01
KL16-09	151.1	154.1	0.75	7500	0.65	1.7	71	15	0.01	16	1	18	0.01	10.2	38	0.01
KL16-09	154.1	157.1	0.63	6300	0.67	0.9	54	10	3	157	0.01	16	0.01	9.0	49	0.01
KL16-09	157.1	160.1	1.87	18700	3.24	3.1	53	15	4	132	3	20	0.01	18.0	53	0.01
KL16-09	160.1	163.1	1.88	18800	5.36	3.4	74	13	2	10	3	22	0.01	18.7	37	0.01
KL16-09	163.1	166.1	1.06	10600	2.08	2.8	84	21	0.01	167	4	16	0.01	11.5	101	0.01
KL16-09	166.1	169.1	1.1	11000	1.64	3.4	64	18	8	13	5	17	0.01	11.0	43	0.01
KL16-09	169.1	172.1	1.28	12800	2.8	1.5	90	37	11	6	2	21	0.01	15.0	35	0.01
KL16-09	172.1	174.6	1.78	17800	2.87	4.9	146	34	0.01	9	21	26	0.01	16.7	30	0.01
KL16-09	174.6	177.7	2.38	23800	2.1	9.7	142	22	3	31	31	22	0.3	17.0	32	0.01
KL16-09	177.7	180.7	1.96	19600	2.63	5.7	120	10	0.01	21	46	34	0.01	16.0	25	0.01
KL16-09	180.7	183.6	2.89	28900	5.57	5.5	107	14	0.01	28	4	23	0.01	23.0	18	0.01
KL16-09	183.6	187.1	2.84	28400	3.77	2.7	116	15	2	4	3	26	0.01	28.0	17	0.01
KL16-09	187.1	190	1.67	16700	1.88	1.8	64	5	6	26	2	14	0.01	14.7	13	0.01
KL16-09	190	192.9	1.31	13100	2.26	2.4	86	13	0.01	31	5	19	0.01	15.7	45	0.01
KL16-09	192.9	195.1	0.46	4600	0.57	1.1	34	10	2	13	3	12	0.01	7.5	16	0.01
KL16-09	195.1	197.6	1.97	19700	2.58	3.3	60	10	2	132	4	16	0.01	30.0	12	0.01
KL16-09	197.6	200.6	2.2	22000	2.31	2.6	87	8	1	36	1	22	0.01	23.0	19	0.01
KL16-09	200.6	203.6	2.19	21900	2.05	2.7	101	8	1	234	1	23	0.01	19.0	32	0.01
KL16-09	203.6	206.6	1.6	16000	1.1	3.6	95	8	3	174	6	23	0.01	21.0	13	0.01
KL16-09	206.6	209.6	1.54	15400	1.18	7.3	68	8	1	361	26	14	0.01	6.7	24	0.01
KL16-09	209.6	211.9	1.22	12200	0.71	4.3	102	9	6	248	10	17	0.5	14.2	20	0.01
KL16-09	211.9	213.9	1.21	12100	0.14	10.5	176	11	14	44	15	67	1.5	5.7	18	0.01
KL16-09	213.9	216.1	0.508	5080	0.34	5.2	1200	23	14	11	18	9	0.01	2.7	18	0.01
KL16-09	216.1	219.2	0.097	970	0.07	1.7	241	25	11	24	2	7	0.01	1.2	19	0.01
KL16-09	219.2	221.6	0.168	1680	0.21	1.3	204	13	8	59	10	25	0.01	4.0	14	0.01
KL16-09	221.6	226.1	0.282	2820	0.2	0.01	650	12	12	62	19	14	0.4	5.7	12	0.01
KL16-09	226.1	227.9	0.72	7200	0.94	1.8	306	10	11	19	16	39	0.2	9.5	19	0.01
KL16-09	227.9	229.8	1.13	11300	1.46	17.2	408	10	10	15	55	79	0.8	14.2	16	0.01
KL16-09	229.8	235.1	0.042	420	0.02	0.01	960	11	10	3	1	18	0.2	0.0	12	0.01
KL16-09	235.1	239.6	0.81	8100	1.84	12.1	20500	16	7	30	162	49	0.9	21.0	16	0.01
KL16-09	239.6	253.1	0.11	1100	0.23	0.6	330	15	7	10	5	9	0.2	0.0	14	0.01
KL16-09	253.1	256.1	0.055	550	0.06	0.01	1430	20	5	2	0.01	5	0.01	0.0	17	0.01
KL16-09	256.1	257.6	0.059	590	0.09	0.01	790	12	2	8	1	4	0.01	0.0	16	0.01
KL16-09	257.6	260.6	1.13	11300	1.02	4.5	830	30	11	10	12	120	1.2	6.2	31	0.01
KL16-09	260.6	263.6	0.0187	187	0.01	0.01	221	15	6	3	0.01	0.01	0.01	0.0	10	0.01
KL16-09	263.6	266.6	0.017	170	0.01	0.01	223	10	3	3	0.01	3	0.01	0.0	11	0.01
KL16-09	266.6	269.6	0.121	1210	0.04	0.01	700	10	5	2	0.01	10	0.3	0.0	12	0.01
KL16-09	269.6	272.6	0.092	920	0.09	0.01	580	12	7	4	1	11	0.01	0.0	14	0.01
KL16-09	272.6	275.6	0.096	960	0.16	0.01	790	13	5	4	38	5	0.2	3.5	16	0.01
KL16-09	275.6	278.6	0.075	750	0.07	0.01	409	14	12	5	0.01	3	0.01	1.7	13	0.01
KL16-09	278.6	281.6	1.11	11100	0.52	14.9	520	12	9	0.01	3	8	0.4	3.0	12	0.01
KL16-09	281.6	284.6	0.46	4600	0.16	7.1	570	10	15	3	2	30	0.01	0.0	14	0.01
KL16-09	284.6	287.6	0.051	510	0.03	0.01	7300	12	10	7	0.01	45	0.6	5.5	16	0.01
KL16-09	287.6	289.1	0.6	6000	0.12	3.9	6100	19	7	10	4	154	0.7	5.0	25	0.01
KL16-09	289.1	293.6	0.85	8500	1.07	3	220	20	2	13	14	60	0.01	9.5	28	0.01
KL16-09	293.6	296.6	0.47	4700	0.44	0.01	118	17	0.01	10	0.01	10	0.01	4.2	18	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL16-09	296.6	299.6	0.57	5700	0.71	1	135	9	0.01	12	0.01	38	0.3	6.8	20	0.01
KL16-09	299.6	302.6	0.91	9100	0.72	1.4	152	8	1	32	0.01	36	0.2	8.0	24	0.01
KL16-09	302.6	305.6	0.75	7500	0.63	1.2	136	14	3	14	0.01	27	0.01	8.5	58	0.01
KL16-09	305.6	308.6	2.06	20600	1.67	3	228	25	14	71	0.01	42	1	14.0	56	0.01
KL16-09	308.6	311.6	2.53	25300	1.71	3.2	281	18	9	12	0.01	67	0.7	35.5	32	0.01
KL16-09	311.6	316.9	1.99	19900	1.1	3.9	284	50	25	134	0.01	54	8.2	13.0	29	0.01
KL16-09	316.9	320.6	1.22	12200	0.73	2.2	147	24	47	67	0.01	40	2.6	7.0	121	0.01
KL16-09	320.6	323.6	1.1	11000	1.04	1.9	197	48	22	21	0.01	46	1.8	8.0	47	0.01
KL16-09	323.6	326.6	1.44	14400	2	1.4	145	13	13	74	0.01	43	0.7	8.0	60	0.01
KL16-09	326.6	330.4	5.09	50900	3.56	5.1	285	13	20	37	0.01	77	0.6	6.3	53	0.01
KL16-09	330.4	333.6	1.76	17600	1.24	2.6	1910	87	19	51	0.01	18	0.9	6.5	99	0.01
KL16-09	333.6	336.6	2.09	20900	1.76	2.4	163	24	23	135	0.01	20	0.01	12.0	286	0.01
KL16-09	336.6	339.6	1.4	14000	1.89	1.9	269	25	30	7	0.01	10	0.2	8.0	86	0.01
KL16-09	339.6	341.3	1.32	13200	1.41	2.7	176	20	15	92	1	9	0.2	5.0	216	0.01
KL16-09	341.3	343.3	2.56	25600	2.4	2.9	206	14	3	112	1	35	0.01	8.0	42	0.01
KL16-09	343.3	346.3	1.34	13400	1.3	1.8	163	22	23	1770	1	9	0.01	7.2	135	0.01
KL16-09	346.3	349.3	0.75	7500	1.09	1.5	262	19	26	800	0.01	6	0.01	4.5	78	0.01
KL16-09	349.3	352.4	1.1	11000	1.59	1.6	113	22	32	87	0.01	10	0.6	6.8	229	0.01
KL16-09	352.4	355.4	0.68	6800	0.97	1.4	159	27	14	769	1	7	0.01	6.8	209	0.01
KL16-09	355.4	358.4	0.58	5800	0.83	1.2	127	23	13	880	0.01	15	0.01	9.1	109	0.01
KL16-09	358.4	361.4	0.62	6200	0.78	1.2	113	30	17	710	0.01	11	0.01	12.2	140	0.01
KL16-09	361.4	364.4	1.46	14600	1.37	2.3	313	48	20	211	1	16	0.01	7.0	90	0.01
KL16-09	364.4	366.7	0.492	4920	0.51	1.4	131	12	7	127	1	20	0.01	7.3	122	0.01
KL16-09	366.7	369.7	0.399	3990	0.2	3.5	4580	3100	21	272	2	18	4.9	17.3	69	0.01
KL16-09	369.7	372.7	0.388	3880	0.5	0.9	203	47	8	173	0.01	13	0.01	3.5	71	0.01
KL16-09	372.7	374.3	0.52	5200	0.34	1.9	550	59	10	87	3	13	0.3	7.3	69	0.01
KL16-09	374.3	377.3	0.299	2990	0.33	1	174	37	6	1100	0.01	13	0.01	6.3	62	0.01
KL16-09	377.3	379	0.197	1970	0.27	0.9	90	27	5	216	0.01	8	0.2	4.0	64	0.01
KL16-09	379	383.6	0.19	1900	0.31	0.8	63	26	5	54	0.01	4	0.3	3.3	63	0.01
KL16-09	383.6	386.6	0.23	2300	0.25	0.9	73	16	7	296	1	15	0.01	4.0	81	0.01
KL16-09	386.6	389.6	0.385	3850	0.41	1.1	151	12	4	134	0.01	15	0.01	4.3	78	0.01
KL16-09	389.6	394.1	0.675	6750	0.85	1.8	263	47	13	2010	1	20	0.4	7.5	116	0.01
KL16-09	394.1	398.6	0.395	3950	0.37	1.2	107	18	3	98	0.01	20	0.01	7.8	91	0.01
KL16-09	398.6	402.6	0.51	5100	0.56	1.2	142	14	4	98	0.01	15	0.01	6.3	89	0.01
KL16-09	402.6	407.6	0.13	1300	0.15	0.7	307	18	5	39	0.01	9	0.01	4.0	63	0.01
KL16-09	407.6	413.6	0.116	1160	0.12	0.8	71	9	5	37	0.01	10	0.01	3.8	62	0.01
KL16-09	413.6	418	0.06	600	0.11	0.7	37	8	3	13	0.01	6	0.01	2.3	60	0.01
KL16-09	418	421	0.08	800	0.1	0.01	48	16	2	15	0.01	5	1.2	1.2	70	0.01
KL16-09	421	424.1	0.049	490	0.08	0.01	42	16	5	28	0.01	5	0.8	1.8	63	0.01
KL16-09	424.1	428.1	0.113	1130	0.12	1.2	38	12	6	23	0.01	10	0.7	0.0	70	0.01
KL16-09	428.1	431.2	0.092	920	0.08	0.01	56	10	8	23	2	6	0.6	1.8	114	0.01
KL16-09	431.2	434	0.109	1090	0.11	0.01	71	16	8	26	1	9	0.4	0.5	87	0.01
KL16-09	434	436.4	0.068	680	0.06	0.01	79	27	7	14	2	5	0.8	3.1	103	0.01
KL16-09	436.4	438.6	0.054	540	0.04	0.01	71	13	6	12	1	6	0.6	2.2	110	0.01
KL16-09	438.6	441.5	0.056	560	0.04	0.01	50	14	7	34	2	6	0.7	1.2	87	0.01
KL16-09	441.5	444	0.0354	354	0.06	0.01	25	5	5	16	1	5	0.6	2.5	84	0.01
KL16-09	444	446.6	0.101	1010	0.06	0.01	47	8	6	14	1	8	0.6	1.5	68	0.01
KL16-09	446.6	449.6	0.083	830	0.07	0.01	67	15	7	23	1	6	0.6	0.7	94	0.01
KL16-09	449.6	452.6	0.11	1100	0.06	0.6	45	12	5	14	2	9	0.4	3.8	99	0.01
KL16-09	452.6	455.6	0.145	1450	0.06	0.01	43	16	5	19	2	9	0.2	3.9	148	0.01
KL16-09	455.6	458.6	0.0058	58	0.01	0.01	40	5	1	0.01	0.01	21	0.01	0.0	55	0.01
KL16-09	458.6	461.6	0.094	940	0.03	0.01	41	10	7	24	1	8	0.5	3.5	92	0.01
KL16-09	461.6	464.6	0.156	1560	0.14	0.01	41	17	3	15	0.01	8	0.6	2.8	85	0.01
KL16-09	464.6	467.6	0.17	1700	0.22	0.01	47	10	7	11	1	10	0.4	5.9	54	0.01
KL16-09	467.6	470.6	0.164	1640	0.16	0.01	37	8	7	54	0.01	16	0.7	6.3	76	0.01
KL16-09	470.6	473.6	0.104	1040	0.15	0.01	25	8	4	25	0.01	10	0.3	4.3	67	0.01
KL16-09	473.6	476.6	0.096	960	0.12	0.01	24	8	3	15	0.01	12	0.2	3.7	48	0.01
KL16-09	476.6	479.6	0.139	1390	0.07	0.01	55	20	6	17	2	8	0.3	4.3	51	0.01
KL16-09	479.6	482.6	0.126	1260	0.13	0.01	38	18	5	36	1	10	0.3	5.5	53	0.01
KL16-09	482.6	485.6	0.105	1050	0.13	0.01	29	7	3	18	0.01	7	0.4	3.0	60	0.01
KL16-09	485.6	488.6	0.251	2510	1.62	0.01	58	5	6	69	1	16	0.01	8.2	77	0.01
KL16-09	488.6	491.6	0.135	1350	0.14	0.01	21	6	2	22	0.01	8	0.01	5.0	64	0.01
KL16-09	491.6	494.6	0.16	1600	0.21	0.6	38	6	2	150	0.01	8	0.01	4.8	58	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL16-09	494.6	497.6	0.097		970	0.12	0.01	27	0.01	2	31	0.01	9	0.2	3.8	65	0.01
KL16-09	497.6	500.6	0.087		870	0.1	0.01	31	5	2	18	1	7	0.4	3.5	96	0.01
KL16-09	500.6	503.6	0.286		2860	0.32	0.01	64	7	4	46	2	12	0.01	8.4	82	0.01
KL16-09	503.6	506.6	0.339		3390	0.46	0.01	49	7	3	73	1	12	0.2	8.7	56	0.01
KL16-09	506.6	509.6	0.134		1340	0.12	0.01	26	8	3	275	0.01	11	0.3	3.8	91	0.01
KL16-09	509.6	512.6	0.107		1070	0.1	0.01	32	6	3	71	0.01	15	0.01	6.1	93	0.01
KL16-09	512.6	515.6	0.243		2430	0.18	0.7	59	10	7	166	1	17	0.3	4.9	106	0.01
KL16-09	515.6	518.6	0.165		1650	0.19	0.01	53	8	6	65	1	12	0.3	2.5	96	0.01
KL16-09	518.6	521.6	0.185		1850	0.13	0.01	45	7	4	60	1	17	0.01	3.8	56	0.01
KL16-09	521.6	524.6	0.137		1370	0.77	0.01	44	6	4	31	2	12	0.01	5.5	68	0.01
KL16-09	524.6	527.6	0.275		2750	0.23	0.01	64	6	8	30	0.01	19	0.3	7.1	108	0.01
KL16-09	527.6	530.6	0.092		920	0.05	0.01	38	6	6	75	0.01	12	0.3	3.0	58	0.01
KL16-09	530.6	533.6	0.085		850	0.06	0.01	30	7	4	38	0.01	10	0.3	3.2	69	0.01
KL16-09	533.6	536.6	0.113		1130	0.11	0.01	31	8	3	23	0.01	12	0.01	3.5	57	0.01
KL16-09	536.6	539.6	0.09		900	0.06	0.01	29	11	3	57	0.01	10	0.01	3.5	40	0.01
KL16-09	539.6	542.8	0.103		1030	0.06	0.01	38	8	6	41	0.01	13	0.01	3.3	57	0.01
KL16-09	542.8	546	0.13		1300	0.08	0.01	56	17	10	25	1	12	0.01	5.2	63	0.01
KL16-09	546	548.6	0.0246		246	0.01	0.01	37	8	1	12	0.01	7	0.3	0.8	58	0.01
KL16-09	548.6	551.6	0.0249		249	0.01	0.01	40	14	1	9	0.01	7	0.3	0.0	31	0.01
KL16-09	551.6	554.6	0.0172		172	0.01	0.01	38	11	1	6	0.01	7	0.6	0.7	32	0.01
KL16-09	554.6	557.6	0.0087		87	0.01	0.01	36	9	1	4	0.01	6	0.3	0.7	26	0.01
KL16-09	557.6	560.6	0.0105		105	0.01	0.01	43	11	1	5	0.01	4	0.01	0.6	21	0.01
KL16-09	560.6	563.6	0.0083		83	0.01	0.01	45	11	1	4	0.01	6	0.01	1.2	21	0.01
KL16-09	563.6	566.6	0.0091		91	0.01	0.01	46	15	1	0.01	0.01	6	0.01	0.0	22	0.01
KL16-09	566.6	569.6	0.0087		87	0.01	0.01	40	14	1	4	0.01	6	0.2	0.5	22	0.01
KL16-09	569.6	572.7	0.0095		95	0.01	0.01	30	10	2	4	0.01	4	0.01	0.0	20	0.01
KL16-09	572.7	575.6	0.081		810	0.05	0.01	52	17	2	5	0.01	10	0.01	1.2	38	0.01
KL16-09	575.6	578.6	0.55		5500	0.42	0.01	83	15	3	28	0.01	20	0.01	6.0	64	0.01
KL16-09	578.6	581.6	0.117		1170	0.11	0.01	50	8	4	25	0.01	9	0.4	1.7	35	0.01
KL16-09	581.6	584.6	0.0209		209	0.01	0.01	34	13	1	8	0.01	4	0.4	1.7	26	0.01
KL16-09	584.6	587.6	0.0172		172	0.01	0.01	37	14	1	6	0.01	6	0.5	2.3	26	0.01
KL16-09	587.6	590.6	0.0142		142	0.01	0.01	36	10	2	7	0.01	3	0.01	0.0	22	0.01
KL16-09	590.6	593.6	0.0122		122	0.01	0.01	37	11	1	5	0.01	4	0.01	0.0	21	0.01
KL16-09	593.6	596.6	0.0149		149	0.01	0.01	39	9	1	3	0.01	6	0.01	0.0	26	0.01
KL16-09	596.6	599.6	0.0134		134	0.01	0.01	39	10	1	3	0.01	10	0.01	1.2	25	0.01
KL16-09	599.6	602.6	0.0142		142	0.01	0.01	41	11	2	3	0.01	5	0.01	1.2	26	0.01
KL16-09	602.6	605.6	0.0107		107	0.01	0.01	44	10	1	0.01	0.01	7	0.01	0.0	118	0.01
KL16-09	605.6	608.6	0.0054		54	0.01	0.01	53	9	1	0.01	0.01	8	0.01	1.2	130	0.01
KL16-09	608.6	611.6	0.005		50	0.01	0.01	60	9	0.01	0.01	0.01	7	0.01	0.7	150	0.01
KL16-09	611.6	614.6	0.0042		42	0.01	0.01	56	8	1	0.01	0.01	10	0.01	0.0	167	0.01
KL18-01	0	3	0.0039		39	0.07	0.6	189	130	8	34	0.01	0.01	0.01	1.5	19	0.01
KL18-01	3	6	0.0046		46	0.03	1.2	111	190	16	26	3	0.01	0.01	4.5	21	0.01
KL18-01	6	9	0.0115		115	0.03	2.9	740	1320	33	33	1	0.01	1.2	17.3	18	0.01
KL18-01	9	12	0.0081		81	0.03	0.5	420	252	21	7	0.01	0.01	0.4	1.7	17	0.01
KL18-01	12	15	0.095		950	0.04	1	300	215	16	12	2	0.01	0.01	2.5	18	0.01
KL18-01	15	18	0.04		400	0.15	1.6	710	197	29	24	2	0.01	0.01	2.0	27	0.01
KL18-01	18	21	0.0167		167	0.15	3.2	640	5750	11	17	1	0.01	0.01	79.0	21	0.01
KL18-01	21	24	0.017		170	0.07	0.9	410	210	19	11	0.01	0.01	0.01	2.0	22	0.01
KL18-01	24	27	0.0303		303	0.05	0.01	500	67	10	6	2	0.01	0.01	2.2	19	0.01
KL18-01	27	30	0.018		180	0.22	1.6	1330	600	14	8	6	0.01	1	7.4	26	0.01
KL18-01	30	33	0.0265		265	0.1	0.8	960	170	23	11	1	0.01	0.6	4.2	15	0.01
KL18-01	33	36	0.156		1560	0.08	0.9	3190	245	23	19	3	12	0.6	7.2	26	0.01
KL18-01	36	39	0.055		550	0.11	1.4	2470	365	22	9	9	3	0.8	5.5	22	0.01
KL18-01	39	41.85	0.47		4700	0.73	1.7	36700	37	30	14	58	38	0.9	32.0	30	0.01
KL18-01	41.85	43.5	0.434		4340	0.58	3.5	10100	1220	29	10	20	25	3	13.3	24	0.01
KL18-01	43.5	45.3	0.4		4000	0.39	3.3	6050	590	25	11	100	18	1.9	12.5	18	0.01
KL18-01	45.3	47.1	0.145		1450	1.93	2	72	31	3	35	1940	2	0.4	36.5	19	0.01
KL18-01	47.1	49.5	0.267		2670	1.89	3.3	80	54	21	357	370	6	0.3	22.3	125	0.01
KL18-01	49.5	52.5	0.57		5700	1.63	2.7	362	47	27	780	9	15	1.4	18.0	47	0.01
KL18-01	52.5	55.6	0.151		1510	0.4	0.01	58	23	17	1710	3	5	0.01	7.0	34	0.01
KL18-01	55.6	58.5	0.165		1650	0.53	0.01	65	31	15	890	2	4	0.2	6.7	26	0.01
KL18-01	58.5	61.5	0.212		2120	0.34	0.01	82	24	5	97	1	4	0.01	1.2	27	0.01
KL18-01	61.5	63.95	0.454		4540	0.61	0.7	450	88	9	121	2	12	0.01	7.7	30	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL18-01	63.95	64.5	1.36	13600	0.48	6.5	6500	204	37	21	32	54	2.6	5.5	21	0.01
KL18-01	64.5	66.3	0.96	9600	1.4	2.4	367	21	11	88	20	16	1.1	8.0	27	0.01
KL18-01	66.3	68.5	0.89	8900	1.75	2.2	89	20	3	45	23	5	0.01	8.7	30	0.01
KL18-01	68.5	69.55	0.72	7200	2.15	2.1	172	18	14	9	31	14	0.01	16.0	25	0.01
KL18-01	69.55	71.5	0.71	7100	1.43	1.3	104	16	11	24	5	8	0.01	9.0	27	0.01
KL18-01	71.5	73.4	1.28	12800	3.15	4.3	93	16	22	22	30	15	0.2	16.5	17	0.01
KL18-01	73.4	74.8	0.95	9500	1.55	1	128	28	18	21	1	15	0.01	84.0	31	0.01
KL18-01	74.8	77.3	0.77	7700	1.02	1.7	97	42	13	83	1	8	0.4	23.5	47	0.01
KL18-01	77.3	80	0.56	5600	1.04	1.1	210	27	3	16	28	5	0.4	16.5	17	0.01
KL18-01	80	82.5	0.351	3510	0.61	0.7	82	27	16	208	1	6	0.3	9.1	36	0.01
KL18-01	82.5	84.7	0.6	6000	0.36	1	148	50	3	27	0.01	14	0.2	11.0	18	0.01
KL18-01	84.7	86.65	0.97	9700	1.56	1.5	394	27	20	54	2	29	0.2	20.7	23	0.01
KL18-01	86.65	90.6	1.07	10700	1.32	1.4	202	28	11	16	3	11	0.3	12.0	47	0.01
KL18-01	90.6	92	1.02	10200	0.83	2	340	24	18	55	2	22	0.2	16.7	12	0.01
KL18-01	92	94.1	0.47	4700	0.52	1.2	9800	32	12	392	3	14	0.01	15.5	13	0.01
KL18-01	94.1	96	0.71	7100	0.61	1	4300	150	10	70	0.01	25	0.01	14.0	14	0.01
KL18-01	96	98	0.056	560	0.06	0.01	328	13	0.01	45	0.01	4	0.01	1.2	8	0.01
KL18-01	98	101.9	0.73	7300	0.75	1.6	4900	15	49	70	2	21	0.3	11.7	33	0.01
KL18-01	101.9	104.4	1.3	13000	1.55	2.2	810	21	17	30	1	40	0.2	30.0	30	0.01
KL18-01	104.4	106.8	2.66	26600	2.52	5.1	1830	24	30	142	1	43	0.01	51.2	29	0.01
KL18-01	106.8	108	0.198	1980	0.72	0.01	193	13	6	375	1	6	0.6	1.9	18	0.01
KL18-01	108	111	0.387	3870	0.52	0.9	184	20	11	660	1	14	0.3	10.1	40	0.01
KL18-01	111	114.5	0.321	3210	0.29	0.6	212	38	10	630	1	15	1.2	8.7	37	0.01
KL18-01	114.5	116.5	0.0192	192	0.04	0.01	255	19	0.01	439	1	0.01	0.6	5.2	0	0.01
KL18-01	116.5	122.5	0.87	8700	1.75	4.7	87400	37	16	209	65	61	0.6	47.2	40	0.01
KL18-01	122.5	127	0.89	8900	1.01	2.5	7400	21	34	104	10	39	1.1	39.0	40	0.01
KL18-01	127	132.5	1.25	12500	1.16	6.2	39500	25	23	111	13	134	1.3	47.5	38	0.01
KL18-01	132.5	134.7	0.202	2020	0.2	1.3	8060	30	11	22	4	41	0.01	17.5	25	0.01
KL18-01	134.7	137.4	1.93	19300	2.05	7.1	19600	43	17	41	7	98	1.1	33.7	38	0.01
KL18-01	137.4	143.3	0.129	1290	0.75	0.01	1100	91	130	810	2	7	0.4	5.4	21	0.42
KL18-01	143.3	146.5	2.09	20900	3.78	4	214	21	2	36	1	34	0.3	19.0	23	0.01
KL18-01	146.5	149.5	3.2	32000	4.47	3.2	220	20	0.01	132	2	50	0.01	22.5	24	0.01
KL18-01	149.5	151	2.7	27000	2.74	4.3	156	41	2	67	1	39	0.2	42.5	15	0.01
KL18-01	151	154	1.07	10700	0.87	1.1	97	12	8	48	0.01	17	0.01	13.7	19	0.01
KL18-01	154	157	2.39	23900	2.93	2.8	1720	10	31	71	1	23	0.01	43.7	20	0.01
KL18-01	157	159.5	1.06	10600	1.64	3.2	600	12	14	59	1	25	0.01	14.5	31	0.01
KL18-01	159.5	162.5	1.62	16200	1.11	3.5	247	7	5	57	0.01	23	0.01	19.5	41	0.01
KL18-01	162.5	164	0.63	6300	0.49	1.2	132	5	4	64	0.01	16	0.01	13.2	46	0.01
KL18-01	164	166.1	2.92	29200	2.49	3.8	268	5	19	149	0.01	30	0.01	23.7	65	0.01
KL18-01	166.1	167.55	1.19	11900	0.69	1.6	90	0.01	12	220	0.01	27	0.01	21.2	47	0.01
KL18-01	167.55	170	1.34	13400	1.14	3.2	139	20	90	1380	1	15	16.5	13.5	59	0.01
KL18-01	170	173	1.04	10400	0.54	4	158	67	39	308	0.01	5	2.9	5.7	53	0.01
KL18-01	173	176	1.35	13500	0.93	11.4	2890	1770	84	180	1	22	21.4	11.5	46	0.14
KL18-01	176	179	1.58	15800	1.37	3.6	620	147	28	102	0.01	29	4.4	10.0	84	0.01
KL18-01	179	182	1.3	13000	1.15	2.3	114	27	9	1010	1	26	0.6	13.0	70	0.01
KL18-01	182	185	1.27	12700	1.92	3.3	53	25	11	284	2	9	0.4	11.0	63	0.01
KL18-01	185	188	0.955	9550	1.4	1.5	36	7	4	95	3	5	0.01	7.0	70	0.01
KL18-01	188	191	1.11	11100	1.76	2.1	31	5	0.01	118	1	6	0.2	7.7	73	0.01
KL18-01	191	194	1.26	12600	1.85	3	80	10	0.01	93	3	6	0.01	8.0	68	0.01
KL18-01	194	197	1.31	13100	1.91	5	840	256	140	268	3	5	13	10.5	45	0.1
KL18-01	197	200	1.16	11600	1.97	3.8	190	92	19	125	5	5	2.3	7.5	54	0.01
KL18-01	200	203	1.3	13000	2	2.3	63	7	2	295	2	11	0.6	15.0	85	0.01
KL18-01	203	206	0.87	8700	1.39	1.7	82	22	1	177	2	5	0.5	10.3	53	0.01
KL18-01	206	209	1.58	15800	2.51	3.5	37	7	0.01	147	3	6	0.2	10.0	86	0.01
KL18-01	209	213.5	1.36	13600	2.03	2.6	57	5	0.01	66	1	7	0.8	8.0	63	0.01
KL18-01	213.5	216.5	1.57	15700	1.64	2.1	65	12	3	59	1	13	0.8	10.0	72	0.01
KL18-01	216.5	219.5	1.39	13900	1.65	2.7	76	0.01	0.01	520	1	16	0.01	9.0	73	0.01
KL18-01	219.5	222.1	1.42	14200	1.33	2.3	89	5	0.01	156	0.01	19	0.01	4.0	74	0.01
KL18-01	222.1	225.5	1.86	18600	2.77	5	46	0.01	4	226	4	14	0.4	3.0	82	0.01
KL18-01	225.5	228.5	1.48	14800	1.93	2.7	39	5	3	73	2	15	0.01	9.5	75	0.01
KL18-01	228.5	231.5	1.1	11000	1.15	3.9	293	142	0.01	152	1	13	2.3	5.2	74	0.01
KL18-01	231.5	234.5	1.22	12200	1	1.6	80	17	3	211	0.01	19	0.6	8.5	101	0.01
KL18-01	234.5	237.5	1.08	10800	0.81	1.4	228	22	3	179	0.01	15	1	3.7	85	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL18-01	237.5	239	1.29	12900	1.27	1.8	94	12	0.01	200	0.01	18	0.4	3.0	83	0.01
KL18-01	239	243.5	0.465	4650	0.38	1.2	327	72	5	47	1	12	0.01	4.7	41	0.01
KL18-01	243.5	245	1.13	11300	0.52	2.4	138	10	0.01	437	0.01	27	0.5	5.3	89	0.01
KL18-01	245	248	1.35	13500	1.2	2	98	12	0.01	60	1	21	0.5	5.0	75	0.01
KL18-01	248	251	0.82	8200	0.64	1.3	65	7	0.01	74	0.01	59	0.01	2.7	71	0.01
KL18-01	251	254	0.93	9300	0.79	1.1	132	22	0.01	84	0.01	18	0.8	3.7	81	0.01
KL18-01	254	257	1.11	11100	1.31	2.6	80	7	0.01	132	2	20	0.01	4.7	92	0.01
KL18-01	257	260	1.31	13100	0.91	2.5	78	0.01	0.01	263	0.01	18	0.01	4.0	80	0.01
KL18-01	260	263	1.03	10300	0.75	1.8	65	5	0.01	790	1	15	0.01	5.5	71	0.01
KL18-01	263	266	1.06	10600	1.5	3	135	20	2	5	1	9	0.01	2.9	13	0.01
KL18-01	266	269	1.16	11600	1.05	1.7	76	5	0.01	218	0.01	24	0.5	4.5	71	0.01
KL18-01	269	272	1.42	14200	1.45	2.6	81	20	0.01	272	1	19	0.3	7.0	82	0.01
KL18-01	272	275	2.28	22800	2.73	3.5	76	15	3	82	2	15	1	7.5	90	0.01
KL18-01	275	278	1.04	10400	0.99	14.7	6800	2510	71	156	2	9	26	6.3	76	0.44
KL18-01	278	281	1.37	13700	1.84	2.6	190	57	0.01	148	2	18	1.6	5.5	86	0.01
KL18-01	281	284	1.35	13500	2.2	2.5	120	40	0.01	114	2	21	0.6	7.5	80	0.01
KL18-01	284	287	1.35	13500	1.52	1.9	87	22	0.01	147	1	24	0.2	2.5	79	0.01
KL18-01	287	290	0.57	5700	0.47	1.2	77	33	0.01	282	0.01	23	0.2	7.7	65	0.01
KL18-01	290	293	1.02	10200	0.97	1.4	96	42	0.01	268	0.01	14	0.3	4.2	68	0.01
KL18-01	293	296	0.53	5300	0.49	1.2	70	37	11	24	0.01	14	0.01	7.7	62	0.01
KL18-01	296	299	1.01	10100	1.07	2.1	96	32	6	40	0.01	17	0.4	8.5	68	0.01
KL18-01	299	302	0.72	7200	0.53	1.2	97	25	0.01	19	0.01	16	0.4	7.7	70	0.01
KL18-01	302	305	1.71	17100	1.72	2	100	20	0.01	68	0.01	19	0.4	3.0	70	0.01
KL18-01	305	308	1.19	11900	1.57	2.1	65	20	0.01	8	1	10	0.01	7.0	85	0.01
KL18-01	308	308.8	0.454	4540	0.89	1.1	40	17	0.01	8	0.01	17	0.01	4.0	104	0.01
KL18-01	308.8	311	0.353	3530	0.41	0.8	235	304	3	6	0.01	3	0.01	3.0	136	0.01
KL18-01	311	314	0.38	3800	1.01	0.7	37	60	22	4	0.01	4	0.01	4.7	122	0.01
KL18-01	314	317	0.35	3500	0.28	2.4	280	202	310	8	4	2	8.7	4.1	96	0.01
KL18-01	317	320	0.451	4510	0.62	1.2	146	82	5	10	1	3	0.01	3.0	123	0.01
KL18-01	320	323	0.381	3810	0.43	0.9	56	35	0.01	20	0.01	3	0.01	2.5	52	0.01
KL18-01	323	326	0.491	4910	0.61	1.3	107	37	0.01	12	1	2	0.01	2.7	54	0.01
KL18-01	326	329	0.88	8800	1.64	3	34	12	1	7	4	2	0.01	6.5	65	0.01
KL18-01	329	330.5	0.92	9200	1.65	2.3	18	0.01	0.01	7	4	3	0.01	3.0	69	0.01
KL18-02	0	4	0.005	50	0.04	0.6	140	133	10	11	0.01	0.01	0.5	2.3	23	0.01
KL18-02	4	7	0.008	80	0.08	4.9	830	570	32	4	12	2	1.3	10.3	22	0.16
KL18-02	7	10	0.0114	114	0.04	3.4	870	890	20	8	3	2	0.6	6.7	17	0.01
KL18-02	10	13	0.0299	299	0.04	0.01	431	840	24	8	1	2	0.5	3.6	20	0.01
KL18-02	13	16	0.076	760	0.09	1.3	760	124	29	26	3	4	0.2	6.0	23	0.01
KL18-02	16	19	0.107	1070	0.23	2.5	1140	275	22	14	2	4	0.4	7.1	23	0.01
KL18-02	19	22	0.0106	106	0.07	0.01	351	67	8	5	3	2	0.8	2.3	20	0.01
KL18-02	22	25	0.0173	173	0.08	0.8	530	410	23	6	3	2	1.3	3.0	17	0.01
KL18-02	25	28	0.0148	148	0.03	1.5	650	440	21	10	4	2	1.1	3.1	20	0.01
KL18-02	28	31	0.129	1290	0.23	1.6	2020	224	150	56	5	8	5.5	12.0	23	0.21
KL18-02	31	34	0.026	260	0.03	0.01	434	249	58	4	1	3	2.9	4.0	17	0.01
KL18-02	34	37	0.32	3200	0.36	3.4	3400	274	160	13	15	15	10.8	21.3	29	0.52
KL18-02	37	40	0.0113	113	0.01	0.01	66	23	2	2	0.01	16	0.01	0.0	17	0.01
KL18-02	40	43	1.17	11700	2.23	3.2	1700	43	29	57	44	35	0.6	24.5	21	0.01
KL18-02	43	46	0.67	6700	2.16	5.6	1550	47	38	297	295	23	3	28.8	48	0.01
KL18-02	46	49	0.65	6500	2.49	4.8	327	53	46	1780	160	10	2.4	34.0	80	0.01
KL18-02	49	52	0.48	4800	1.07	3.6	186	25	47	660	10	9	3.1	22.8	91	0.01
KL18-02	52	55	0.5	5000	1.32	3.4	196	36	26	940	9	11	1.7	14.5	95	0.01
KL18-02	55	58	1.47	14700	3.84	3	410	24	10	210	46	27	0.7	21.2	42	0.01
KL18-02	58	61	1.23	12300	1.54	5.3	194	20	17	110	70	16	0.3	15.8	43	0.01
KL18-02	61	64	0.78	7800	2.05	3.3	100	12	16	21	50	11	0.2	13.3	32	0.01
KL18-02	64	67	0.76	7600	2.58	1.9	113	12	13	55	14	11	0.3	11.6	47	0.01
KL18-02	67	70	0.76	7600	1.12	1.6	92	14	9	29	8	9	0.3	10.1	71	0.01
KL18-02	70	73	0.57	5700	1.03	1.6	92	12	7	67	8	15	0.01	13.2	61	0.01
KL18-02	73	76	0.37	3700	1.04	0.8	161	7	6	47	4	9	0.01	7.3	23	0.01
KL18-02	76	79	0.68	6800	1.39	1.4	100	12	13	5	3	9	0.2	8.4	20	0.01
KL18-02	79	82	0.42	4200	0.59	0.5	78	10	7	202	1	7	0.3	8.3	45	0.01
KL18-02	82	85	0.97	9700	0.85	1.3	204	19	3	85	1	17	0.01	19.0	20	0.01
KL18-02	85	88	0.46	4600	0.56	0.5	150	16	15	9	0.01	10	0.01	5.0	23	0.01
KL18-02	88	91	0.7	7000	1.06	0.8	207	13	29	16	1	11	0.3	10.2	41	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL18-02	91	94	0.41	4100	0.57	0.7	90	7	38	360	2	6	0.9	8.4	23	0.01
KL18-02	94	97	0.156	1560	0.27	0.01	73	12	16	61	1	5	0.2	2.9	41	0.01
KL18-02	97	100	0.55	5500	2.68	2.3	74	19	14	122	22	6	0.4	10.2	22	0.01
KL18-02	100	103	0.095	950	0.86	0.8	69	30	30	100	1	7	0.4	6.9	40	0.01
KL18-02	103	105.7	0.0217	217	0.33	0.01	170	25	16	135	0.01	5	0.4	4.0	60	0.01
KL18-02	105.7	109	0.48	4800	0.5	2.4	21500	18	14	45	7	51	2	18.3	70	0.01
KL18-02	109	112	0.09	900	0.18	0.8	4300	60	11	4	8	6	1.6	4.7	29	0.01
KL18-02	112	114.3	0.178	1780	0.2	11.4	7500	3300	14	6	82	6	0.7	30.8	27	0.01
KL18-02	114.3	118	0.49	4900	0.52	0.6	320	15	6	33	0.01	18	0.01	8.7	21	0.01
KL18-02	118	121	0.85	8500	0.96	1	287	6	1	132	1	25	0.01	13.4	27	0.01
KL18-02	121	124	1.79	17900	1.13	2.2	800	11	4	192	0.01	23	0.01	31.0	22	0.01
KL18-02	124	127	0.0116	116	0.01	0.01	67	17	0.01	2	0.01	16	0.01	0.0	16	0.01
KL18-02	127	130.5	0.75	7500	0.57	1.3	520	33	7	140	0.01	52	0.2	32.5	70	0.01
KL18-02	130.5	133.5	0.53	5300	0.31	0.9	400	13	4	105	0.01	37	0.01	24.8	73	0.01
KL18-02	133.5	136.5	0.8	8000	0.58	1.4	107	11	3	42	0.01	69	0.01	15.6	91	0.01
KL18-02	136.5	139.3	2.78	27800	1.4	6.7	1050	840	6	354	9	77	0.01	33.9	96	0.01
KL18-02	139.3	142.5	0.81	8100	1.18	1.7	62	19	2	193	0.01	13	0.01	6.8	86	0.01
KL18-02	142.5	145.5	1.68	16800	2.79	3.4	56	21	0.01	133	3	11	0.01	18.0	100	0.01
KL18-02	145.5	148.5	1.62	16200	2.48	4.2	45	15	4	56	2	10	0.01	16.0	127	0.01
KL18-02	148.5	151.5	1.11	11100	0.39	6.1	57	13	13	58	2	8	0.01	7.0	101	0.01
KL18-02	151.5	154.5	1.19	11900	0.5	6.3	56	20	22	69	4	13	0.01	4.0	121	0.01
KL18-02	154.5	157.5	1.2	12000	0.48	4.6	36	18	5	85	3	12	0.01	4.0	134	0.01
KL18-02	157.5	160.5	1.16	11600	0.96	3.1	39	18	0.01	86	3	12	0.01	14.0	127	0.01
KL18-02	160.5	163.5	1.11	11100	1.33	4.3	31	9	1	88	4	13	0.01	11.0	124	0.01
KL18-02	163.5	166.5	1.08	10800	1.06	2.3	40	11	3	126	2	11	0.01	7.5	123	0.01
KL18-02	166.5	169.5	1.57	15700	0.37	3.2	30	13	2	94	3	11	0.01	14.0	120	0.01
KL18-02	169.5	172.5	1.32	13200	0.39	3.4	49	21	5	52	4	12	0.01	5.5	159	0.01
KL18-02	172.5	175.5	1.22	12200	0.35	3.8	48	27	7	56	2	14	0.01	4.0	134	0.01
KL18-02	175.5	178.5	0.96	9600	0.36	2.7	45	20	4	43	2	16	0.01	4.0	106	0.01
KL18-02	178.5	181.5	0.97	9700	1.19	1.5	25	13	2	102	1	11	0.01	9.0	104	0.01
KL18-02	181.5	184.5	0.99	9900	1.27	1.2	30	9	2	66	3	11	0.01	7.5	126	0.01
KL18-02	184.5	187.5	1.1	11000	0.7	1.7	28	13	4	89	1	10	0.01	5.0	102	0.01
KL18-02	187.5	190.5	1.25	12500	1.53	2	13	6	2	88	2	10	0.01	7.5	98	0.01
KL18-02	190.5	193.5	0.88	8800	1.12	2	27	11	1	123	1	11	0.01	7.2	94	0.01
KL18-02	193.5	196.5	0.96	9600	0.61	1.7	35	10	5	75	0.01	8	0.01	5.5	102	0.01
KL18-02	196.5	199.5	1.09	10900	1.4	1.8	27	9	4	89	0.01	8	0.01	7.5	100	0.01
KL18-02	199.5	202	1.1	11000	2.31	1.9	17	7	1	138	3	7	0.01	13.0	91	0.01
KL18-02	202	205	1.75	17500	2.47	5.1	17	8	1	38	6	11	0.01	15.5	80	0.01
KL18-02	205	208	1.95	19500	2.2	5	26	9	2	65	7	11	0.01	11.0	81	0.01
KL18-02	208	211	1.37	13700	1.37	3	18	7	4	59	3	8	0.01	11.0	103	0.01
KL18-02	211	214	1.69	16900	0.95	5.6	920	1450	66	131	2	10	10.6	10.0	76	0.24
KL18-02	214	217	1.63	16300	1.31	2.3	25	23	4	153	3	10	0.01	5.0	80	0.01
KL18-02	217	220	1.32	13200	0.99	1.5	25	8	3	226	0.01	11	0.01	11.5	106	0.01
KL18-02	220	223	1.72	17200	1.55	2.2	30	7	3	108	1	17	0.01	13.0	100	0.01
KL18-02	223	226	1.32	13200	1.04	1.4	40	15	5	219	0.01	13	0.01	8.0	80	0.01
KL18-02	226	229	1.11	11100	0.91	1.6	31	13	4	313	0.01	11	0.01	5.8	74	0.01
KL18-02	229	232	1.12	11200	0.64	1.9	64	21	24	338	0.01	13	0.01	6.5	80	0.01
KL18-02	232	235	1.14	11400	0.89	1.6	34	17	5	308	0.01	14	0.01	6.0	97	0.01
KL18-02	235	238	1.5	15000	0.82	1.4	127	17	1	330	0.01	46	0.01	15.5	105	0.01
KL18-02	238	241	1.12	11200	0.58	1.4	124	16	2	325	0.01	55	0.8	3.5	49	0.01
KL18-02	241	244	2.98	29800	1.14	3.1	154	17	0.01	358	0.01	56	0.2	3.3	45	0.01
KL18-02	244	247	2.17	21700	1.04	2.6	147	15	3	345	1	58	0.2	11.2	50	0.01
KL18-02	247	250	1.02	10200	0.5	1	142	22	1	250	1	39	0.01	6.9	38	0.01
KL18-02	250	253	1.42	14200	1.68	1.3	140	15	3	109	0.01	42	0.2	14.5	50	0.01
KL18-02	253	256	1.04	10400	0.98	1.8	325	26	1	65	4	37	0.01	20.0	92	0.01
KL18-02	256	259	1.52	15200	1.74	4	12000	450	14	19	20	31	1.6	32.5	104	0.01
KL18-02	259	262	0.97	9700	2.44	5.6	11700	1340	11	106	26	27	2.8	32.7	65	0.01
KL18-02	262	265	0.725	7250	10.1	3.8	890	500	21	3	8	28	0.9	9.4	151	0.01
KL18-02	265	268	0.72	7200	10	6.2	385	148	21	62	5	64	1.4	22.2	102	0.01
KL18-02	268	271	0.154	1540	0.18	0.01	146	29	2	2	1	30	0.3	4.5	38	0.01
KL18-02	271	274	0.58	5800	3.3	2.3	170	80	19	13	2	43	1.6	16.4	76	0.01
KL18-02	274	277	0.85	8500	2.52	2.6	151	62	24	9	1	89	1.7	11.4	78	0.01
KL18-02	277	280	1.07	10700	3.79	5.7	113	34	13	154	2	70	0.2	29.0	70	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL18-02	280	283	3.52	35200	7.62	22.3	327	24	17	120	2	63	0.2	106.0	85	0.01
KL18-02	283	286	2.09	20900	4.4	12	262	28	17	144	24	37	0.01	52.4	72	0.01
KL18-02	286	289	1.33	13300	3.65	7.1	283	17	10	183	7	51	0.01	50.0	67	0.01
KL18-02	289	290.3	1.46	14600	5.42	10.7	345	20	38	227	0.01	59	0.2	40.0	49	0.01
KL18-02	290.3	293.5	0.98	9800	2.48	4	190	18	58	78	0.01	29	0.01	17.0	32	0.01
KL18-02	293.5	296.5	1.33	13300	1.1	6.1	680	8	24	112	0.01	46	0.2	30.5	42	0.01
KL18-02	296.5	299.5	1.77	17700	2.05	8.8	164	10	54	113	1	59	1.9	17.0	71	0.01
KL18-02	299.5	302.5	1.61	16100	1.89	4	3300	12	39	25	0.01	48	0.6	114.0	34	0.01
KL18-02	302.5	304.6	0.62	6200	0.67	2.1	170	24	38	7	0.01	25	0.7	29.2	28	0.01
KL18-02	304.6	308.5	0.0394	394	0.05	0.01	75	12	9	3	0.01	2	0.01	1.8	10	0.01
KL18-02	308.5	311.5	0.0091	91	0.01	0.01	28	17	1	0.01	0.01	2	0.2	0.0	9	0.01
KL18-02	311.5	314.5	0.0129	129	0.01	0.01	106	13	6	2	0.01	2	0.2	1.5	10	0.01
KL18-02	314.5	317.5														
KL18-02	317.5	320.5														
KL18-02	320.5	323														
KL18-03	0	3	0.0123	123	0.05	1	2700	510	15	8	0.01	0.01	0.7	6.8	15	0.22
KL18-03	3	6	0.0206	206	0.06	1.4	150	50	15	8	1	0.01	0.8	2.6	16	0.01
KL18-03	6	9	0.0254	254	0.2	3.2	430	127	66	15	4	0.01	3	6.2	26	0.26
KL18-03	9	12	0.05	500	0.14	4.2	2610	790	150	30	8	0.01	5.5	14.3	19	0.66
KL18-03	12	15	0.106	1060	0.12	4.9	1080	241	440	31	2	0.01	7.9	8.3	27	0.16
KL18-03	15	18	0.438	4380	0.11	5.2	3700	1210	1430	25	5	0.01	22	11.2	18	0.33
KL18-03	18	21	1.47	14700	0.29	18.9	7350	2700	3550	24	8	11	150	73.7	30	0.61
KL18-03	21	24	0.071	710	0.18	2.7	620	112	130	11	3	0.01	3.6	16.2	22	0.13
KL18-03	24	27	0.204	2040	0.25	2.4	1060	87	170	9	4	2	4.6	10.9	25	0.01
KL18-03	27	30	0.0289	289	0.13	1.3	830	114	48	10	2	0.01	2.6	4.1	17	0.01
KL18-03	30	33	0.125	1250	0.15	0.8	2270	63	290	5	1	0.01	19.8	5.8	22	0.01
KL18-03	33	36	0.0327	327	0.08	0.5	840	98	16	4	3	0.01	1	6.2	26	0.01
KL18-03	36	39	0.1	1000	0.29	0.7	410	42	14	4	5	3	0.4	4.1	14	0.01
KL18-03	39	42	0.0145	145	0.09	0.01	194	20	15	13	2	2	0.6	8.0	18	0.01
KL18-03	42	45	0.217	2170	0.23	1.9	4290	36	20	39	7	9	1	8.7	34	0.01
KL18-03	45	48	0.65	6500	1.69	4.5	13100	25	29	6	26	43	3.2	19.2	22	0.01
KL18-03	48	51	0.155	1550	0.62	2.1	1900	440	35	7	5	0.01	2.6	14.0	18	0.01
KL18-03	51	54	0.56	5600	1.17	1.4	1610	31	20	101	22	14	0.9	13.9	18	0.01
KL18-03	54	57	1.21	12100	1.45	6.5	15800	800	460	111	29	25	88	41.3	70	0.34
KL18-03	57	61	0.448	4480	3.64	8.1	1760	610	330	66	5	4	28	14.7	58	0.26
KL18-03	61	64	0.278	2780	3.67	10.6	3570	910	110	68	5	6	12	31.0	57	0.21
KL18-03	64	67	0.214	2140	2.35	5.4	2850	600	61	71	3	6	7.3	16.8	26	0.25
KL18-03	67	70	0.86	8600	3.51	14.8	10500	3200	170	11	64	10	98	18.0	34	0.23
KL18-03	70	73	0.88	8800	12.3	13.3	10700	4400	110	28	14	5	22.6	16.0	28	0.32
KL18-03	73	76	1.59	15900	2.2	15.6	5100	1880	34	65	247	14	16.2	62.0	40	0.01
KL18-03	76	79	0.492	4920	1.23	3.1	1210	1290	11	54	7	11	3.9	18.2	35	0.01
KL18-03	79	82	0.83	8300	1.65	2.8	247	56	22	29	9	9	0.5	16.0	25	0.01
KL18-03	82	85	0.482	4820	1.53	1.2	277	174	23	32	4	8	0.4	9.0	33	0.01
KL18-03	85	88	0.256	2560	0.8	0.8	87	18	9	101	2	6	0.4	9.5	24	0.01
KL18-03	88	91	0.88	8800	1.18	1.2	194	20	12	8	1	13	0.01	10.8	19	0.01
KL18-03	91	94	0.74	7400	1.03	1.7	187	20	42	84	1	10	0.01	14.6	15	0.01
KL18-03	94	95.8	0.8	8000	0.79	1.5	251	16	31	212	1	18	0.01	11.8	17	0.01
KL18-03	95.8	98.6	0.386	3860	0.61	0.5	131	17	11	188	0.01	7	0.7	7.5	59	0.01
KL18-03	98.6	101.5	0.362	3620	0.4	1	151	15	24	480	0.01	12	0.5	15.1	54	0.01
KL18-03	101.5	103	1.04	10400	0.72	2.2	400	21	22	600	1	53	0.3	19.2	36	0.01
KL18-03	103	106	1.17	11700	0.84	1.2	343	10	9	355	0.01	47	0.01	19.8	24	0.01
KL18-03	106	109	1.03	10300	0.65	1.4	231	12	22	197	1	30	0.01	8.8	16	0.01
KL18-03	109	112	0.198	1980	0.27	0.01	158	12	12	59	0.01	31	0.01	5.3	29	0.01
KL18-03	112	115	0.86	8600	0.64	1.1	272	12	10	1670	1	41	0.3	15.2	23	0.01
KL18-03	115	118	0.24	2400	0.42	0.7	540	14	14	68	2	24	0.5	19.5	17	0.01
KL18-03	118	121	0.368	3680	0.32	0.7	278	13	12	26	3	47	0.2	44.0	16	0.01
KL18-03	121	123.7	0.376	3760	0.21	1.2	3080	32	6	38	2	32	0.2	35.0	15	0.01
KL18-03	123.7	125.5	0.425	4250	0.65	1	100	10	2	21	1	38	0.01	40.0	23	0.01
KL18-03	125.5	127.5	0.55	5500	0.83	1.6	123	8	5	76	1	43	0.01	29.0	27	0.01
KL18-03	127.5	129	0.72	7200	1.26	1.4	90	8	3	93	0.01	40	0.01	18.2	25	0.01
KL18-03	129	131.5	1.55	15500	1.38	2.1	375	34	0.01	65	1	75	0.01	12.0	31	0.01
KL18-03	131.5	134.5	2.29	22900	2.72	3.9	356	39	1	348	1	81	0.01	30.5	33	0.01
KL18-03	134.5	137.5	2.73	27300	3.01	4.1	125	24	5	206	9	45	0.01	17.0	53	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL18-03	137.5	140.5	2.4	24000	2.07	3.6	78	65	30	59	0.01	40	0.6	17.0	83	0.01
KL18-03	140.5	143.5	2.57	25700	1.38	2.5	560	187	260	780	1	51	5.9	26.0	58	0.79
KL18-03	143.5	146.2	4.22	42200	4.29	4.5	76	32	50	152	1	36	0.4	21.0	67	0.5
KL18-03	146.2	149.5	0.71	7100	0.26	2.3	265	293	140	608	0.01	8	29	6.0	70	0.32
KL18-03	149.5	152.5	1.76	17600	0.4	2.5	54	17	12	950	1	20	0.5	16.0	58	0.11
KL18-03	152.5	155.5	2.29	22900	0.58	3.3	50	27	14	450	0.01	22	0.01	19.0	59	0.12
KL18-03	155.5	158.5	2.68	26800	0.66	3.1	50	26	12	1380	0.01	19	0.6	21.0	77	0.15
KL18-03	158.5	161.5	1.86	18600	0.37	1.9	59	19	16	1300	0.01	13	1.1	12.0	69	0.01
KL18-03	161.5	164.5	1.68	16800	1.05	3.2	71	23	4	1050	0.01	20	0.2	15.0	70	0.14
KL18-03	164.5	166.9	3.47	34700	2.91	4.6	245	100	7	2280	0.01	74	0.01	10.0	93	0.01
KL18-03	166.9	168.6	0.96	9600	0.62	1.7	159	15	1	189	0.01	50	0.4	4.4	87	0.01
KL18-03	168.6	170.5	2.7	27000	2.94	7.5	540	14	42	46	4	118	3	22.0	51	0.01
KL18-03	170.5	173.5	0.69	6900	1.36	5.2	10600	101	78	27	37	61	7.8	4.8	76	0.01
KL18-03	173.5	175	0.174	1740	0.6	3.1	1710	189	120	10	44	19	24	10.7	70	0.01
KL18-03	175	178	0.63	6300	1.16	3.7	12800	20	30	8	11	120	4.8	9.4	82	0.01
KL18-03	178	179.5	0.128	1280	0.21	2.3	7400	146	230	15	30	35	62	10.7	93	0.01
KL18-03	179.5	182.1	0.26	2600	0.29	4.6	114000	167	78	3	5	230	11.2	49.0	43	0.01
KL18-03	182.1	184	0.0256	256	0.11	3.3	1600	700	33	6	5	6	1.3	1.2	30	0.01
KL18-03	184	187	0.0262	262	0.38	14.7	3070	12400	70	8	4	7	23	4.9	40	0.01
KL18-03	187	190	0.0228	228	0.37	16.9	8900	19400	130	4	28	9	8.8	8.9	31	0.01
KL18-03	190	193	0.0122	122	0.19	6.5	1700	3100	200	6	0.01	6	13	14.1	37	0.01
KL18-03	193	196	0.0086	86	0.01	0.8	387	260	29	5	0.01	4	1.1	1.5	26	0.01
KL18-03	196	199	0.0121	121	0.01	0.5	335	172	16	5	0.01	6	1.1	0.6	26	0.01
KL18-03	199	202	0.0096	96	0.01	0.01	137	50	5	3	0.01	4	0.3	0.0	18	0.01
KL18-03	202	205	0.008	80	0.01	9.7	950	2820	17	3	0.01	4	12.2	0.0	20	0.01
KL18-03	205	208	0.0136	136	0.01	3.3	4150	2050	21	4	0.01	7	4.6	1.3	23	0.01
KL18-03	208	211	0.035	350	0.01	1.5	1550	412	19	4	0.01	7	3.6	0.6	22	0.01
KL18-03	211	214	0.0149	149	0.01	0.01	1030	140	8	7	0.01	7	0.8	0.0	18	0.01
KL18-03	214	217	0.021	210	0.01	0.01	520	44	7	88	0.01	6	0.8	0.5	14	0.01
KL18-03	217	220	0.0341	341	0.01	0.01	910	20	7	38	1	8	0.3	0.5	12	0.01
KL18-03	220	223	0.062	620	0.08	0.6	2340	21	11	173	0.01	8	0.3	0.7	14	0.01
KL18-03	223	226	0.0286	286	0.01	0.01	140	19	4	23	1	6	0.6	0.0	14	0.01
KL18-03	226	229	0.0273	273	0.02	0.01	386	21	5	44	0.01	6	0.3	0.0	13	0.01
KL18-03	229	232	0.005	50	0.02	0.01	71	16	9	9	0.01	2	0.01	0.0	13	0.01
KL18-03	232	235	0.0062	62	0.01	0.01	88	29	11	72	0.01	3	1.5	0.0	6	0.01
KL18-04	0	6	0.0202	202	0.06	1.6	2450	580	37	4	2	0.01	1.3	3.2	14	0.33
KL18-04	6	9	0.0063	63	0.02	0.01	195	78	8	5	1	0.01	0.3	1.9	15	0.01
KL18-04	9	11.4	0.0092	92	0.02	0.01	184	95	9	4	0.01	0.01	0.5	1.9	16	0.01
KL18-04	11.4	13.5	0.0193	193	0.04	0.01	393	227	20	9	1	0.01	1.3	2.6	18	0.01
KL18-04	13.5	16.5	0.006	60	0.01	0.01	257	148	23	12	1	0.01	0.01	1.8	14	0.01
KL18-04	16.5	18.8	0.0074	74	0.02	0.01	400	160	1	26	1	0.01	0.9	3.8	18	0.01
KL18-04	18.8	20	0.0141	141	0.03	0.01	262	23	37	8	0.01	0.01	0.6	2.3	20	0.01
KL18-04	20	22.5	0.028	280	0.06	1.2	740	95	90	23	5	2	1.9	4.4	17	0.2
KL18-04	22.5	25.3	0.0056	56	0.01	0.6	272	181	23	7	1	0.01	0.4	2.8	13	0.01
KL18-04	25.3	27	0.0128	128	0.14	3.9	960	1230	120	4	16	0.01	1.7	25.0	14	0.17
KL18-04	27	28.5	0.0291	291	0.1	2.5	630	590	170	9	11	0.01	2.3	13.2	14	0.12
KL18-04	28.5	30.8	0.0208	208	0.07	0.01	500	40	44	5	1	0.01	1.1	3.1	21	0.1
KL18-04	30.8	33	0.0113	113	0.02	0.01	280	142	13	9	2	0.01	0.01	2.5	15	0.01
KL18-04	33	35.4	0.102	1020	0.16	0.01	2100	133	35	11	11	3	0.5	6.6	22	0.01
KL18-04	35.4	37.5	0.11	1100	2.31	149	39600	42500	54	27	10	3	15.5	238.0	23	0.75
KL18-04	37.5	40.5	0.081	810	0.16	2.2	2050	750	11	13	3	3	1	8.1	19	0.01
KL18-04	40.5	43.5	0.093	930	0.21	4.8	5400	1290	350	14	8	5	12.9	10.6	21	0.4
KL18-04	43.5	46.5	0.008	80	0.01	0.7	400	219	14	4	1	0.01	0.4	1.5	19	0.01
KL18-04	46.5	49.5	0.01	100	0.04	0.5	416	196	10	6	4	0.01	0.4	1.9	17	0.01
KL18-04	49.5	52.6	0.309	3090	0.17	1.9	1090	510	27	13	6	2	4.1	4.8	18	0.01
KL18-04	52.6	55.5	0.0379	379	0.13	0.5	356	55	18	14	1	0.01	0.5	4.0	24	0.01
KL18-04	55.5	58.5	0.0257	257	0.06	0.01	238	143	16	8	1	0.01	0.2	3.0	17	0.01
KL18-04	58.5	60	0.058	580	0.16	0.01	980	30	23	14	3	0.01	0.8	4.4	25	0.01
KL18-04	60	63	0.36	3600	0.86	2.1	5100	17	40	35	12	15	0.6	9.1	36	0.01
KL18-04	63	65.7	0.99	9900	1.88	2.2	2500	22	33	80	57	31	5.2	22.5	16	0.01
KL18-04	65.7	67.5	0.37	3700	1	2.5	132	37	10	240	4	8	0.2	12.3	58	0.01
KL18-04	67.5	69.5	0.8	8000	1.81	4	360	125	35	330	6	14	1.2	10.4	60	0.01
KL18-04	69.5	72.7	0.223	2230	0.17	2.2	880	720	39	154	7	8	1.2	6.9	69	0.13

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL18-04	72.7	75.7	0.392		3920	0.51	4.6	1250	870	82	187	6	13	3.5	15.0	66	0.2
KL18-04	75.7	78.7	0.2		2000	0.38	0.5	219	55	8	250	2	10	0.4	3.3	53	0.01
KL18-04	78.7	80.2	0.282		2820	0.25	0.5	118	23	15	220	2	10	0.2	4.3	50	0.01
KL18-04	80.2	83.1	1.28		12800	2.3	1.8	371	24	6	16	22	33	0.6	22.3	26	0.01
KL18-04	83.1	84.7	0.62		6200	1.1	0.7	168	18	9	77	17	9	0.01	10.6	29	0.01
KL18-04	84.7	87.7	0.8		8000	2.96	1.3	198	31	11	33	9	16	0.9	11.5	17	0.01
KL18-04	87.7	90.7	0.86		8600	2.02	2.1	269	78	8	65	16	10	0.4	8.6	29	0.01
KL18-04	90.7	93.7	0.465		4650	1.02	3.2	440	153	17	70	4	11	0.9	8.2	33	0.01
KL18-04	93.7	96.7	0.528		5280	0.76	6.7	1150	356	41	50	6	13	1.9	8.2	32	0.01
KL18-04	96.7	99.7	1.06		10600	2.08	3.4	163	17	15	25	2	20	0.3	21.5	23	0.01
KL18-04	99.7	102.7	0.58		5800	1.05	0.6	119	16	5	11	1	14	0.01	7.8	16	0.01
KL18-04	102.7	105.7	0.448		4480	0.75	0.5	200	18	7	51	3	12	0.01	8.9	18	0.01
KL18-04	105.7	107.5	1.02		10200	1.62	1.3	303	13	10	11	2	30	0.01	19.0	18	0.01
KL18-04	107.5	110	1.57		15700	1.68	1.7	323	18	14	40	0.01	36	0.01	42.0	18	0.01
KL18-04	110	111.7	0.503		5030	0.61	0.6	198	23	15	400	0.01	12	0.3	9.6	33	0.01
KL18-04	111.7	114.7	0.115		1150	0.86	0.01	71	12	27	1100	1	4	1	10.1	42	0.01
KL18-04	114.7	117.4	0.165		1650	0.47	0.8	850	137	55	750	2	6	2.2	10.7	46	0.01
KL18-04	117.4	120.5	0.146		1460	0.41	0.6	283	19	27	560	1	6	0.6	9.2	21	0.01
KL18-04	120.5	123.7	1.28		12800	1.63	2.8	4200	33	28	62	4	22	1	28.0	35	0.14
KL18-04	123.7	126.7	1.02		10200	1.23	4.8	5300	22	21	14	7	35	0.5	35.0	21	0.01
KL18-04	126.7	128.6	0.645		6450	0.36	3.8	9700	16	20	11	4	25	0.8	14.8	21	0.01
KL18-04	128.6	130.6	1.34		13400	1.27	4.9	1750	10	12	44	5	43	0.4	41.5	18	0.01
KL18-04	130.6	132.7	0.97		9700	0.7	5.2	4300	17	18	14	14	50	7	27.0	29	0.01
KL18-04	132.7	135.7	1.07		10700	1.25	3	1640	14	22	68	3	54	2.9	36.2	22	0.01
KL18-04	135.7	138.7	1.08		10800	1.11	2.6	1020	27	22	150	2	63	3.6	25.5	17	0.01
KL18-04	138.7	141.7	0.78		7800	0.59	1.6	970	15	27	31	2	31	0.5	12.0	21	0.01
KL18-04	141.7	144.7	1.09		10900	0.8	2.8	3300	12	12	16	2	69	0.7	23.0	14	0.01
KL18-04	144.7	147.2	2.01		20100	1.01	3.5	6000	12	14	153	1	68	0.01	85.3	60	0.01
KL18-04	147.2	149.5	1.81		18100	1.12	2.6	13600	9	27	18	2	108	0.01	21.0	52	0.01
KL18-04	149.5	151.7	2.21		22100	1.08	5.8	19500	14	58	42	0.01	120	0.2	10.0	75	0.01
KL18-04	151.7	153.7	1.32		13200	1.05	10.6	12700	208	48	122	3	105	3.5	16.0	109	0.01
KL18-04	153.7	156.7	1.7		17000	2.32	10.4	28600	27	69	295	21	78	0.6	78.0	106	0.01
KL18-04	156.7	159.7	1.16		11600	2.68	5.4	4700	19	85	128	9	103	0.8	35.3	83	0.01
KL18-04	159.7	162.7	1.4		14000	0.88	3.1	1100	12	220	27	0.01	92	2.6	7.0	75	0.01
KL18-04	162.7	165.5	1.21		12100	0.9	2.2	1710	20	300	16	0.01	54	6.8	10.5	125	0.01
KL18-04	165.5	167.9	0.0246		246	0.15	0.01	2100	79	42	12	0.01	9	4.9	3.1	20	0.01
KL18-04	167.9	169.7	0.56		5600	1.15	3.7	20700	11	210	3	2	60	2.7	0.0	60	0.1
KL18-04	169.7	171.7	0.0176		176	0.14	0.01	510	9	20	6	0.01	0.01	0.6	1.0	42	0.01
KL18-04	171.7	174.7	0.165		1650	0.22	3.9	6300	600	57	38	7	13	3.1	14.7	35	0.01
KL18-04	174.7	177.7	0.0261		261	0.15	2.1	790	259	52	11	3	0.01	3.9	2.7	36	0.01
KL18-04	177.7	180.7	0.057		570	0.14	1.5	520	83	34	4	0.01	0.01	1.4	2.5	18	0.01
KL18-04	180.7	183.7	0.0024		24	0.05	0.5	560	27	10	3	0.01	0.01	0.6	3.0	17	0.01
KL18-04	183.7	186.7	0.006		60	0.01	0.01	114	22	20	2	0.01	0.01	1	1.1	13	0.01
KL18-04	186.7	189.5	0.0201		201	0.04	0.01	205	19	26	3	0.01	0.01	2.1	2.2	16	0.01
KL18-04	189.5	192.5	0.0068		68	0.04	3.2	1410	510	20	2	0.01	0.01	1.5	1.8	14	0.01
KL18-04	192.5	195.7	0.0142		142	0.1	5	2300	600	47	4	0.01	0.01	3.8	4.7	27	0.01
KL18-04	195.7	198.7	0.0017		17	0.01	0.01	243	70	10	5	0.01	0.01	0.3	1.0	17	0.01
KL18-04	198.7	201.7	0.0024		24	0.07	0.5	790	354	8	14	0.01	0.01	0.9	3.6	35	0.01
KL18-04	201.7	204.7	0.0024		24	0.02	0.01	94	20	7	12	0.01	0.01	0.01	0.0	15	0.01
KL18-04	204.7	206.2	0.0016		16	0.04	0.01	128	56	6	4	0.01	0.01	0.01	0.9	15	0.01
KL18-04	206.2	210.4	0.003		30	0.06	0.01	223	149	9	24	1	0.01	0.2	2.1	16	0.01
KL18-04	210.4	213.4	0.0015		15	0.04	0.01	202	135	7	5	0.01	0.01	0.3	0.9	14	0.01
KL18-04	213.4	216.2	0.0039		39	0.09	3.1	1630	850	25	10	4	3	1.8	4.4	26	0.01
KL18-05	0	3	0.0213		213	0.07	2.9	1400	1540	13	6	1	2	1.6	6.6	16	0.1
KL18-05	3	5	0.0068		68	0.09	7.1	4590	6250	9	3	4	3	3.4	18.1	14	0.14
KL18-05	5	7.7	0.006		60	0.01	0.01	220	212	2	6	1	2	0.4	1.4	14	0.01
KL18-05	7.7	9.3	0.004		40	0.01	0.01	134	171	5	12	1	0.01	0.3	0.7	18	0.01
KL18-05	9.3	11	0.0032		32	0.02	0.01	80	75	16	11	1	2	0.4	0.7	19	0.01
KL18-05	11	14	0.004		40	0.01	0.01	128	74	8	11	1	3	0.3	1.4	17	0.01
KL18-05	14	17	0.0029		29	0.01	0.01	117	88	4	12	0.01	2	0.4	1.2	14	0.01
KL18-05	17	20	0.0032		32	0.01	0.01	123	81	6	8	2	2	0.2	1.2	17	0.01
KL18-05	20	23	0.0031		31	0.02	1.3	259	187	10	4	1	0.01	0.01	1.1	16	0.01
KL18-05	23	26	0.003		30	0.01	0.01	201	165	7	6	0.01	0.01	0.4	2.4	16	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL18-05	26	28.6	0.0043		43	0.03	0.01	190	123	13	7	0.01	2	0.5	2.9	18	0.01
KL18-05	28.6	31.8	0.0168		168	0.05	0.01	274	63	24	23	1	2	0.01	2.9	18	0.01
KL18-05	31.8	34.8	0.0254		254	0.06	4.2	790	318	14	14	10	4	2.6	8.0	15	0.01
KL18-05	34.8	37.8	0.0047		47	0.01	0.01	87	90	6	0.01	0.01	3	0.01	3.1	10	0.01
KL18-05	37.8	41	0.0048		48	0.05	0.8	345	560	14	8	0.01	4	0.4	7.4	16	0.01
KL18-05	41	44	0.02		200	0.05	1	550	930	18	29	4	0.01	0.5	7.6	20	0.01
KL18-05	44	47	0.047		470	0.09	0.6	840	75	15	37	1	2	0.3	5.2	22	0.01
KL18-05	47	50	0.0185		185	0.22	7.6	1540	1180	28	24	8	0.01	2.4	19.5	33	0.37
KL18-05	50	53	0.0056		56	0.09	1.6	239	142	6	12	2	0.01	0.2	2.9	21	0.01
KL18-05	53	56	0.005		50	0.02	0.01	397	350	5	17	0.01	0.01	0.5	3.3	18	0.01
KL18-05	56	59	0.0054		54	0.02	0.01	450	15	9	7	0.01	0.01	0.01	0.6	21	0.01
KL18-05	59	61	0.0023		23	0.03	0.01	206	130	11	4	1	0.01	0.2	1.8	19	0.01
KL18-05	61	63.5	0.0049		49	0.01	0.01	370	530	6	16	1	0.01	0.01	5.3	16	0.01
KL18-05	63.5	66.5	0.0132		132	0.02	0.01	520	120	14	14	0.01	2	0.01	2.5	13	0.01
KL18-05	66.5	69.3	0.0388		388	0.09	0.01	1720	40	18	4	17	0.01	0.9	4.9	25	0.01
KL18-05	69.3	71	0.0143		143	0.06	0.01	338	0.01	15	4	0.01	2	0.01	2.8	17	0.01
KL18-05	71	74	0.0164		164	0.05	0.01	115	0.01	22	3	0.01	2	0.3	4.9	21	0.01
KL18-05	74	77	0.24		2400	0.79	0.7	21800	40	31	14	5	23	0.3	18.7	23	0.01
KL18-05	77	79.5	0.64		6400	1.21	1.4	2590	33	38	36	8	18	0.2	9.0	27	0.01
KL18-05	79.5	82.6	1.28		12800	1.85	3.1	490	39	11	740	12	32	0.8	31.0	59	0.01
KL18-05	82.6	84.3	0.119		1190	0.43	1.1	387	92	12	500	2	11	0.5	5.4	47	0.1
KL18-05	84.3	86	0.157		1570	0.37	0.5	68	21	3	410	1	14	0.5	2.8	45	0.01
KL18-05	86	89	0.161		1610	0.59	0.6	61	13	10	370	1	6	0.5	7.4	41	0.01
KL18-05	89	92	1.07		10700	1.58	2.8	10600	21	43	450	85	38	1.7	29.9	28	0.01
KL18-05	92	95	1.47		14700	2.23	3.4	2400	10	9	350	5	31	0.3	23.8	34	0.01
KL18-05	95	98	2.33		23300	2.29	3.2	760	16	8	210	12	36	1	42.0	19	0.01
KL18-05	98	101	0.67		6700	1.26	5.1	490	980	60	230	3	15	4	30.5	31	0.01
KL18-05	101	104	3.06		30600	4.67	3.7	332	19	18	35	16	41	1.2	37.8	37	0.01
KL18-05	104	107	0.73		7300	1.78	2.2	2610	19	10	250	42	37	0.4	20.0	15	0.01
KL18-05	107	109.5	0.59		5900	1.71	2.4	342	34	24	190	3	24	1.4	16.2	35	0.01
KL18-05	109.5	112.5	0.95		9500	1.27	2.8	960	205	120	180	8	27	8.3	35.4	28	0.01
KL18-05	112.5	114.5	0.377		3770	0.49	1.5	195	20	39	350	14	13	2.9	8.9	27	0.01
KL18-05	114.5	118.1	0.88		8800	1.34	8.5	3800	1320	82	350	6	32	0.9	23.5	26	0.1
KL18-05	118.1	120.8	1.67		16700	2.33	1.8	227	8	21	379	0.01	31	0.4	23.5	25	0.01
KL18-05	120.8	123	0.64		6400	0.68	0.01	132	17	16	710	1	13	0.6	21.4	43	0.01
KL18-05	123	125	0.236		2360	0.68	0.01	160	26	25	3500	7	8	0.7	15.6	58	0.01
KL18-05	125	128	0.366		3660	0.7	0.01	103	13	6	1000	2	11	0.3	15.3	57	0.01
KL18-05	128	131	0.445		4450	1.16	0.7	820	26	110	760	6	13	2.2	14.5	49	0.01
KL18-05	131	134	1.1		11000	1.82	5.4	14700	25	77	349	32	63	4.2	45.2	27	0.01
KL18-05	134	137	0.64		6400	0.51	2.7	9000	22	62	131	9	56	1.4	32.7	23	0.01
KL18-05	137	140	0.75		7500	0.56	3	2150	18	120	389	24	47	1.6	13.7	20	0.01
KL18-05	140	143	1.25		12500	1.23	3.4	550	10	14	365	3	51	1.1	30.0	24	0.01
KL18-05	143	146	1.17		11700	0.72	3.6	800	10	16	128	3	47	1.5	40.8	23	0.01
KL18-05	146	149	0.151		1510	0.24	1.6	4020	10	21	250	16	13	0.5	7.5	15	0.01
KL18-05	149	152	0.115		1150	0.41	6.2	8800	680	26	117	88	10	4.3	14.1	17	0.01
KL18-05	152	155	0.113		1130	0.43	14.4	3920	1370	110	104	58	8	3.4	16.0	29	0.1
KL18-05	155	158	0.162		1620	0.86	17.9	7700	1810	250	149	64	10	11	20.0	83	0.1
KL18-05	158	161	0.21		2100	0.64	17.3	23000	4580	320	195	58	11	10.2	41.8	73	0.01
KL18-05	161	164	0.0355		355	0.13	2.3	2760	510	77	32	11	5	1.4	10.2	22	0.01
KL18-05	164	167.3	0.011		110	0.2	0.01	540	40	31	9	2	7	1	3.1	22	0.01
KL18-05	167.3	170.3	0.0303		303	0.11	0.01	990	26	23	22	2	6	1	6.3	32	0.01
KL18-05	170.3	173	0.14		1400	0.51	1.6	13500	15	37	3	7	22	1	0.9	36	0.01
KL18-05	173	175.8	0.059		590	0.14	0.01	340	10	9	3	1	7	0.2	7.1	20	0.01
KL18-05	175.8	179	0.0206		206	0.09	0.01	1660	16	5	4	1	10	0.2	5.3	27	0.01
KL18-05	179	182	0.164		1640	0.21	2.1	820	60	32	3	1	10	0.3	12.6	39	0.01
KL18-05	182	185	0.0091		91	0.05	0.01	1150	141	17	7	2	4	0.01	5.0	28	0.01
KL18-05	185	187.8	0.0057		57	0.02	0.01	220	15	7	3	0.01	3	0.2	1.4	19	0.01
KL18-05	187.8	190.4	0.0291		291	0.07	0.01	1090	14	37	3	0.01	8	0.8	7.1	18	0.01
KL18-05	190.4	193.4	0.0108		108	0.06	0.01	920	12	26	2	1	3	0.4	2.7	20	0.01
KL18-05	193.4	195.1	0.0147		147	0.1	3.3	3320	960	31	6	40	4	0.8	15.0	21	0.01
KL18-05	195.1	198.2	0.0084		84	0.1	0.01	690	173	18	3	1	3	0.01	16.6	18	0.01
KL18-05	198.2	203	0.002		20	0.04	0.01	930	121	14	3	3	2	0.01	4.7	18	0.01
KL18-05	203	206	0.0055		55	0.06	0.01	780	39	16	13	0.01	0.01	0.01	3.5	20	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL18-05	206	209	0.0012		12	0.01	0.01	216	13	9	4	0.01	0.01	0.01	0.7	27	0.01
KL18-05	209	212	0.0014		14	0.05	0.01	354	8	12	8	0.01	0.01	0.01	1.2	25	0.01
KL18-05	212	215	0.0018		18	0.03	0.01	263	9	15	7	0.01	2	0.01	1.2	24	0.01
KL18-05	215	218	0.0135		135	0.03	0.01	412	28	23	38	0.01	4	4.4	2.0	26	0.01
KL18-05	218	221	0.0043		43	0.19	0.01	225	54	33	8	0.01	0.01	0.01	0.7	19	0.01
KL18-05	221	224	0.004		40	0.05	0.01	271	50	17	57	36	0.01	0.01	2.2	23	0.01
KL18-05	224	227	0.0265		265	0.06	0.01	950	26	12	33	0.01	3	0.01	3.7	25	0.01
KL18-06	0	9	0.0029		29	0.03	0.5	225	219	3	10	1	0.01	0.6	3.1	19	0.01
KL18-06	9	12	0.0232		232	0.1	7.6	2020	2350	42	9	28	0.01	1.5	8.3	28	0.01
KL18-06	12	15	0.0069		69	0.08	2.6	460	510	43	11	4	0.01	1.5	9.7	20	0.01
KL18-06	15	17.4	0.0046		46	0.04	1.5	402	327	31	13	2	0.01	1	5.3	23	0.01
KL18-06	17.4	20.3	0.0058		58	0.02	1.2	392	540	13	18	1	3	0.3	3.2	13	0.01
KL18-06	20.3	21.9	0.0075		75	0.05	2.3	910	940	22	19	3	0.01	0.6	12.5	21	0.01
KL18-06	21.9	23.9	0.0122		122	0.04	1.6	1370	1420	28	58	2	2	1.4	11.2	23	0.01
KL18-06	23.9	26	0.0081		81	0.17	1.8	930	400	26	17	7	3	2.1	4.6	61	0.01
KL18-06	26	27.9	0.0026		26	0.05	2	203	540	28	11	16	3	1.1	5.1	22	0.01
KL18-06	27.9	30	0.0047		47	0.01	0.8	273	475	8	43	0.01	5	0.2	7.4	23	0.01
KL18-06	30	33	0.0033		33	0.1	2	620	890	19	12	3	0.01	1.1	2.5	20	0.01
KL18-06	33	35	0.0009		9	0.02	0.6	94	147	6	6	0.01	0.01	0.8	11.0	17	0.01
KL18-06	35	37.5	0.0028		28	0.4	3.2	4140	600	55	7	5	0.01	1.4	4.8	16	1.77
KL18-06	37.5	40.1	0.0008		8	0.02	0.9	172	323	6	16	1	2	0.4	5.1	16	0.01
KL18-06	40.1	42	0.0012		12	0.02	0.01	200	131	2	20	0.01	0.01	0.01	2.2	13	0.01
KL18-06	42	44.8	0.001		10	0.02	0.01	123	160	7	10	0.01	0.01	0.6	3.4	22	0.01
KL18-06	44.8	48	0.0204		204	0.03	1.2	365	220	23	171	9	0.01	0.5	4.3	14	0.01
KL18-06	48	49.6	0.0274		274	0.03	1.1	650	113	20	53	7	2	1	3.0	16	0.01
KL18-06	49.6	51	0.051		510	0.03	1.8	820	211	35	16	18	3	0.01	3.5	21	0.01
KL18-06	51	54	0.0121		121	0.01	1.9	480	341	15	8	18	0.01	0.3	3.1	11	0.01
KL18-06	54	57	0.0089		89	0.01	1.3	310	323	15	3	14	4	0.4	2.6	21	0.01
KL18-06	57	60	0.0094		94	0.01	1.4	346	348	16	4	10	0.01	0.3	1.9	23	0.01
KL18-06	60	62.2	0.0049		49	0.01	0.9	221	215	7	3	6	2	0.2	0.9	20	0.01
KL18-06	62.2	65.2	0.006		60	0.01	0.7	205	107	4	2	5	0.01	0.01	2.4	18	0.01
KL18-06	65.2	68.3	0.0042		42	0.01	0.01	228	159	6	4	2	0.01	0.3	1.8	17	0.01
KL18-06	68.3	70.4	0.0053		53	0.01	0.01	221	120	10	2	1	0.01	0.2	1.5	17	0.01
KL18-06	70.4	72.8	0.0057		57	0.01	0.9	239	286	12	8	2	0.01	0.4	6.6	18	0.01
KL18-06	72.8	75	0.0109		109	0.01	1.1	490	293	25	11	2	0.01	0.7	9.6	16	0.01
KL18-06	75	78.6	0.0231		231	0.01	1.4	1030	341	54	4	2	0.01	1.4	6.1	18	0.01
KL18-06	78.6	79.5	0.0032		32	0.01	0.8	195	280	4	0.01	6	0.01	0.2	1.6	17	0.01
KL18-06	79.5	81	0.006		60	0.01	0.6	314	580	10	9	2	0.01	0.01	5.2	16	0.01
KL18-06	81	84	0.0043		43	0.05	1.5	990	376	42	11	12	0.01	0.5	6.5	17	0.01
KL18-06	84	87	0.0013		13	0.01	1	316	304	8	5	0.01	0.01	0.4	5.5	17	0.01
KL18-06	87	90	0.0026		26	0.01	0.9	186	210	11	7	1	2	0.2	3.5	20	0.01
KL18-06	90	93	0.0074		74	0.03	0.6	275	56	8	5	4	4	0.2	4.8	21	0.01
KL18-06	93	96	0.185		1850	0.79	4.4	8200	136	32	4	105	19	5	14.9	22	0.01
KL18-06	96	99	0.0283		283	0.14	2	6600	166	13	5	99	14	3	9.8	18	0.01
KL18-06	99	102	0.21		2100	0.36	2.4	11300	88	11	3	19	19	0.9	13.2	17	0.01
KL18-06	102	105	0.0317		317	0.06	0.01	630	20	17	2	4	3	0.4	0.8	23	0.01
KL18-06	105	108	0.23		2300	0.14	2.2	760	21	12	23	2	9	0.7	4.2	21	0.01
KL18-06	108	111	0.0042		42	0.01	0.01	215	10	7	0.01	4	3	0.3	0.0	17	0.01
KL18-06	111	114	0.0144		144	0.02	0.01	232	16	8	12	2	0.01	0.3	0.0	21	0.01
KL18-06	114	117	0.0401		401	0.04	1.2	400	91	11	9	5	0.01	0.5	0.6	25	0.01
KL18-06	117	120	0.0026		26	0.13	0.6	212	20	11	0.01	2	0.01	1.1	1.0	19	0.01
KL18-06	120	123	0.0037		37	0.02	0.8	283	210	6	4	1	0.01	0.3	4.9	11	0.01
KL18-06	123	126	0.0072		72	0.03	1.6	235	840	32	4	6	2	0.9	17.7	17	0.01
KL18-06	126	129	0.0022		22	0.02	3	430	1300	28	40	16	3	1	10.0	15	0.01
KL18-06	129	132	0.063		630	0.03	2	950	490	14	4	6	2	1.1	18.3	23	0.01
KL18-06	132	135	0.0037		37	0.02	0.7	490	308	52	13	2	3	3.7	4.0	23	0.01
KL18-06	135	138	0.039		390	0.06	0.6	490	187	22	0.01	2	0.01	3.1	4.4	19	0.01
KL18-06	138	140.8	0.057		570	0.17	25.7	26300	12000	95	5	40	2	14.9	98.0	25	0.01
KL18-06	140.8	143.8	0.0108		108	0.08	5.7	4740	5000	28	6	18	2	9.8	106.0	17	0.01
KL18-06	143.8	145.5	0.0017		17	0.18	1.5	650	530	25	2	3	0.01	3.5	16.8	19	0.01
KL18-06	145.5	147	0.0011		11	0.03	0.7	500	550	12	5	0.01	0.01	2.7	40.0	15	0.01
KL18-06	147	150	0.0016		16	0.03	0.8	1040	1080	8	3	0.01	0.01	3.3	23.0	18	0.01
KL18-06	150	153	0.0016		16	0.18	2.1	1450	1050	22	5	2	0.01	7.2	29.0	25	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL18-06	153	156	0.0024		24	0.04	0.8	354	354	13	5	0.01	0.01	4.4	10.7	18	0.01
KL18-06	156	159	0.0013		13	0.04	0.6	470	670	14	17	0.01	0.01	4.1	18.4	10	0.01
KL18-06	159	162	0.0029		29	0.03	2.6	300	1000	14	16	20	2	2.1	33.0	15	0.01
KL18-06	162	165	0.058		580	0.06	7.7	5400	11100	64	38	4	4	10.8	85.3	16	0.12
KL18-06	165	168	0.0238		238	0.12	24.6	8600	7000	77	15	0.01	0.01	43	37.0	19	0.86
KL18-06	168	171	0.0029		29	0.03	0.8	430	540	19	8	0.01	3	2.2	9.9	42	0.01
KL18-06	171	174	0.0129		129	0.06	3.6	610	1150	55	7	42	2	1.7	20.8	19	0.12
KL18-06	174	177	0.0018		18	0.02	1.2	315	620	27	2	5	2	0.6	5.1	16	0.21
KL18-06	177	179	0.0057		57	0.01	2.7	660	108	16	3	7	4	1.2	9.6	17	0.01
KL18-06	179	181.7	0.012		120	0.13	6.8	4900	2600	21	6	70	2	6.6	18.1	16	0.34
KL18-06	181.7	183.9	0.161		1610	0.54	4.9	10300	260	79	96	93	20	14	19.8	45	0.75
KL18-06	183.9	186	0.086		860	0.4	2.2	910	74	94	860	28	9	15.7	11.0	40	0.23
KL18-06	186	189	0.091		910	0.49	2.3	660	128	200	1300	26	8	17	24.5	168	0.15
KL18-06	189	192	0.084		840	0.27	0.8	490	55	56	730	5	8	7.8	8.8	101	0.17
KL18-06	192	195	0.307		3070	0.44	1.3	1650	135	280	390	115	15	15.7	17.9	87	0.4
KL18-06	195	198	0.074		740	0.39	1.1	700	116	51	740	16	8	4.7	14.3	115	0.17
KL18-06	198	200.8	0.056		560	0.11	0.6	1000	94	51	162	2	5	6.8	8.8	172	0.01
KL18-06	200.8	202.9	0.057		570	0.31	0.5	3090	42	57	850	14	8	2.5	10.5	50	0.01
KL18-06	202.9	205	0.67		6700	2.04	1.1	700	25	47	147	12	42	4	11.9	26	0.01
KL18-06	205	206.8	0.7		7000	1.2	2.4	55000	39	13	84	93	180	1.4	88.0	56	0.2
KL18-06	206.8	209.8	2.82		28200	1.68	6.7	86000	230	42	176	330	224	8.1	143.0	52	0.2
KL18-06	209.8	212.8	2.2		22000	1.07	4	1490	88	26	192	120	56	5.2	43.0	82	0.1
KL18-06	212.8	216	0.61		6100	1	2.5	3530	88	39	730	300	50	3.8	47.0	62	0.01
KL18-06	216	219	0.52		5200	0.85	2.8	3840	65	55	1470	410	61	1.5	80.0	88	0.01
KL18-06	219	222	0.49		4900	0.69	1.7	3700	42	29	530	40	47	1.2	29.0	97	0.01
KL18-06	222	225	0.3		3000	0.55	1.2	5900	30	25	53	38	51	3.9	16.3	64	0.01
KL18-06	225	228	0.44		4400	0.43	1.6	10900	37	23	7	4	41	3.5	16.1	29	0.01
KL18-06	228	231	0.34		3400	0.69	4.9	18600	145	39	6	30	30	6.3	42.0	116	0.01
KL18-06	231	234	0.04		400	0.74	26.3	1810	3670	43	13	355	4	1.2	58.8	45	0.1
KL18-06	234	237	0.0113		113	0.1	10.2	2420	2900	28	21	65	2	1	16.2	32	0.1
KL18-06	237	240	0.0165		165	0.08	2.1	1810	1740	43	18	14	3	0.3	12.9	52	0.01
KL18-06	240	243	0.102		1020	0.36	52.9	19900	25500	56	41	267	5	5.3	192.0	79	0.2
KL18-06	243	245.8	0.0123		123	0.07	2.4	1800	1130	35	45	16	2	0.3	10.9	51	0.1
KL18-06	245.8	247.7	0.09		900	0.42	10.5	30400	3900	83	210	116	13	1.6	110.0	39	0.01
KL18-06	247.7	251.9	0.0083		83	0.06	7.7	8100	5400	13	11	2	0.01	9.1	9.9	28	0.01
KL18-06	251.9	256.3	0.0082		82	0.04	1.3	1270	640	12	6	3	0.01	0.5	5.3	26	0.01
KL18-06	256.3	259.5	0.0058		58	0.04	1.6	1300	1170	14	2	2	0.01	1.1	6.3	18	0.01
KL18-06	259.5	264	0.0126		126	0.09	6.5	5040	8300	20	15	5	0.01	6	24.0	20	0.14
KL18-06	264	267	0.0114		114	0.07	6.5	2830	3750	22	13	5	0.01	3.7	12.0	21	0.1
KL18-06	267	270	0.021		210	0.08	8.1	3540	2720	18	29	5	0.01	4.3	16.7	30	0.1
KL18-06	270	273	0.0115		115	0.14	18.4	4500	4200	17	6	1	0.01	14.6	18.9	35	0.1
KL18-06	273	276	0.0143		143	0.46	98.8	4900	8600	40	6	0.01	0.01	34	37.9	33	0.12
KL18-06	276	278.3	0.25		2500	1.24	134	114000	102000	500	400	80	6	60	307.0	56	0.19
KL18-06	278.3	280.7	0.0106		106	0.25	10.2	2720	3100	47	31	1	4	4.8	25.5	54	0.12
KL18-06	280.7	284.3	0.0058		58	0.14	9	2550	2300	22	5	0.01	7	5.9	18.3	30	0.01
KL18-06	284.3	286.5	0.046		460	0.67	60.1	42800	23300	155	21	7	0.01	48	115.0	129	0.16
KL18-06	286.5	288	0.012		120	0.16	9.3	1780	1640	21	4	0.01	3	3.8	9.8	39	0.01
KL18-06	288	291	0.004		40	0.06	3.8	580	960	17	5	0.01	2	1.5	7.7	40	0.01
KL18-06	291	293.8	0.0041		41	0.05	1.6	258	440	18	5	0.01	3	1.4	4.2	40	0.01
KL18-06	293.8	296.6	0.0029		29	0.04	1.1	243	303	6	3	0.01	2	0.8	4.3	36	0.01
KL18-06	296.6	299.6	0.0033		33	0.04	1.5	246	297	20	5	0.01	2	1.4	5.2	38	0.01
KL18-06	299.6	302.5	0.0271		271	0.07	10.5	4600	10800	34	7	2	5	14.6	18.1	31	0.12
KL18-06	302.5	304.5	0.0161		161	0.22	21	6000	6700	95	8	1	3	18.5	19.5	58	0.01
KL18-06	304.5	308	0.0023		23	0.04	2.5	640	570	14	2	0.01	0.01	2	2.3	30	0.01
KL18-06	308	309.2	0.0278		278	0.4	30.2	4900	14500	71	77	0.01	3	22	80.0	126	0.14
KL18-06	309.2	311.8	0.0217		217	0.15	6.5	860	1100	56	20	0.01	0.01	3.3	8.8	40	0.01
KL18-06	311.8	314.5	0.008		80	0.07	5.8	475	1270	34	17	0.01	0.01	5.8	6.7	45	0.01
KL18-06	314.5	317.4	0.0153		153	0.09	3.6	1520	3100	100	10	5	3	10	7.0	35	0.01
KL18-06	317.4	321	0.0068		68	0.08	6.1	520	580	59	6	3	3	9.9	4.5	42	0.01
KL18-06	321	324	0.0022		22	0.09	9.3	560	790	42	6	0.01	2	7	7.2	33	0.01
KL18-06	324	326.3	0.003		30	0.07	8	2360	2820	46	6	0.01	2	6.7	20.5	26	0.01
KL18-07	0	3	0.081		810	0.06	14.5	8200	2900	110	11	5	5	13.6	8.0	14	0.8
KL18-07	3	6	0.01		100	0.02	0.01	352	312	15	10	1	6	0.8	4.3	18	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL18-07	6	9	0.0097		97	0.06	0.01	124	91	17	14	3	4	0.8	1.5	21	0.01
KL18-07	9	12	0.0199		199	0.07	3.2	1420	239	30	16	5	4	0.6	8.7	23	0.01
KL18-07	12	15	0.008		80	0.04	0.01	215	32	13	15	1	3	0.3	3.0	18	0.01
KL18-07	15	17.7	0.0174		174	0.05	1.3	470	209	16	18	9	4	0.4	9.0	22	0.01
KL18-07	17.7	19.5	0.0204		204	0.05	0.01	367	67	25	40	3	7	0.4	1.5	26	0.01
KL18-07	19.5	21.6	0.0187		187	0.1	1.9	530	190	23	76	29	5	0.6	4.3	28	0.01
KL18-07	21.6	24	0.0114		114	0.09	5.5	308	186	13	41	41	2	0.2	2.8	18	0.01
KL18-07	24	27	0.0207		207	0.16	3.5	1920	51	18	10	17	5	0.4	5.5	20	0.01
KL18-07	27	29.3	0.0263		263	0.09	1.8	1520	25	16	14	5	5	0.3	0.8	20	0.01
KL18-07	29.3	31.5	0.0098		98	0.04	0.5	470	21	13	10	1	3	0.4	1.5	23	0.01
KL18-07	31.5	34.5	0.0076		76	0.03	0.01	420	19	10	13	1	2	1.2	3.3	28	0.01
KL18-07	34.5	38.3	0.0121		121	0.04	0.01	620	25	15	10	2	5	0.7	4.5	27	0.01
KL18-07	38.3	40.5	0.0178		178	0.02	0.01	750	24	16	8	3	4	0.9	3.3	28	0.01
KL18-07	40.5	43.5	0.11		1100	0.06	0.01	1130	125	13	8	3	10	1.9	10.4	32	0.01
KL18-07	43.5	47.5	0.26		2600	0.11	0.9	3350	15	36	23	4	26	6.1	38.3	34	0.01
KL18-07	47.5	51	0.82		8200	0.67	0.5	940	20	35	19	3	33	3.7	41.5	27	0.01
KL18-07	51	54	0.39		3900	0.68	1	13900	12	24	10	7	60	5.3	70.7	31	0.01
KL18-07	54	57	0.29		2900	0.92	0.9	14000	7	26	9	12	65	1.8	11.8	21	0.01
KL18-07	57	60.7	0.76		7600	1.24	2	2900	7	24	9	5	49	4	10.8	28	0.01
KL18-07	60.7	63.7	0.36		3600	0.67	0.9	9200	9	17	7	28	35	2.6	14.0	31	0.01
KL18-07	63.7	66.7	0.46		4600	0.39	2.1	3500	30	24	10	4	24	1.2	7.5	24	0.01
KL18-07	66.7	69.2	1.15		11500	1.29	2.2	910	10	6	27	4	37	0.7	13.1	41	0.01
KL18-07	69.2	72.7	0.0257		257	0.5	0.01	167	44	9	665	4	9	1.4	5.0	58	0.01
KL18-07	72.7	75.7	0.064		640	0.27	1.3	960	283	34	1125	10	7	8.6	12.0	174	0.01
KL18-07	75.7	78.7	0.085		850	0.44	0.6	258	144	35	950	5	10	6	7.0	115	0.01
KL18-07	78.7	81.7	0.179		1790	0.51	1.5	300	90	13	43	1	7	0.8	5.0	45	0.01
KL18-07	81.7	84.9	0.33		3300	0.49	2.1	560	348	38	695	4	12	5.1	9.3	93	0.01
KL18-07	84.9	87.7	1.32		13200	3.08	3.5	3200	62	11	9	6	31	1.5	22.5	18	0.01
KL18-07	87.7	90.7	0.38		3800	0.6	0.6	50600	76	23	70	6	76	1.2	19.0	25	0.1
KL18-07	90.7	93.7	0.49		4900	1.31	0.8	480	56	23	660	4	16	0.9	9.5	24	0.01
KL18-07	93.7	96.7	0.9		9000	1.57	1.2	10900	113	15	55	5	48	0.7	17.0	32	0.01
KL18-07	96.7	99.7	0.66		6600	1.19	1	830	182	9	26	2	19	0.2	9.0	21	0.01
KL18-07	99.7	102.7	0.38		3800	0.87	0.01	147	60	17	83	3	8	0.7	5.0	66	0.01
KL18-07	102.7	105.7	0.62		6200	1.59	1.7	267	165	12	191	2	12	0.6	12.8	58	0.01
KL18-07	105.7	108.7	0.57		5700	1.19	0.01	238	53	16	173	3	10	0.2	8.0	50	0.01
KL18-07	108.7	111.7	1.09		10900	2	1.8	187	7	21	330	7	22	0.3	14.8	26	0.01
KL18-07	111.7	114.7	0.92		9200	1.44	0.6	520	70	24	73	1	20	0.2	22.5	20	0.01
KL18-07	114.7	117.7	0.64		6400	0.7	0.01	124	19	5	11	1	12	0.01	5.3	27	0.01
KL18-07	117.7	120.7	1.06		10600	1.42	0.6	278	5	5	12	2	21	0.01	6.3	13	0.01
KL18-07	120.7	123.7	0.35		3500	0.41	0.01	580	14	5	57	4	8	0.01	5.0	22	0.01
KL18-07	123.7	126.7	0.58		5800	1.76	0.01	191	11	17	27	9	12	0.01	7.5	17	0.01
KL18-07	126.7	129.7	0.95		9500	2.89	2.8	96	0.01	25	76	19	11	0.01	9.9	18	0.01
KL18-07	129.7	132.7	0.28		2800	0.54	0.01	223	7	31	184	1	10	0.01	5.8	23	0.01
KL18-07	132.7	134.4	0.25		2500	0.43	0.01	70	24	22	151	0.01	10	0.2	2.5	21	0.01
KL18-07	134.4	136.5	0.48		4800	0.38	0.6	102	7	0.01	101	1	5	0.01	4.0	72	0.01
KL18-07	136.5	138.7	0.6		6000	0.75	0.01	96	7	9	101	1	6	0.01	5.5	43	0.01
KL18-07	138.7	141.7	0.54		5400	0.75	0.01	89	8	15	83	0.01	8	0.4	4.0	47	0.01
KL18-07	141.7	144.7	0.171		1710	0.1	0.6	27	13	3	60	2	3	0.01	2.5	21	0.01
KL18-07	144.7	147.7	0.072		720	0.06	0.01	51	23	4	381	1	2	0.01	1.6	18	0.01
KL18-07	147.7	150.7	0.095		950	0.17	0.01	52	8	4	420	1	5	0.01	1.0	17	0.01
KL18-07	150.7	153.7	2.35		23500	1.81	4.5	29600	14	22	1150	1	105	0.01	16.0	42	0.01
KL18-07	153.7	159.7	2.09		20900	0.92	2.5	1290	5	31	770	1	98	0.01	17.5	18	0.01
KL18-07	159.7	171.7	2.06		20600	1.47	3.8	261	0.01	4	154	8	40	3.4	9.0	23	0.01
KL18-07	171.7	174	3.59		35900	3.44	3.7	308	0.01	3	530	2	41	0.9	20.0	24	0.01
KL18-07	174	177	1.83		18300	1.56	1.3	143	0.01	2	455	1	38	0.2	10.0	11	0.01
KL18-07	177	180	2.31		23100	1.61	1.7	141	0.01	10	314	1	42	0.01	14.5	15	0.01
KL18-07	180	183	2.41		24100	1.65	1.8	172	0.01	0.01	146	1	60	0.01	18.0	12	0.01
KL18-07	183	186	2.72		27200	0.9	3.7	430	0.01	5	27	1	103	0.2	15.0	12	0.01
KL18-07	186	189	2.03		20300	0.98	3.4	287	0.01	43	43	2	75	0.4	9.0	11	0.01
KL18-07	189	192	1.25		12500	1.11	1.8	131	0.01	65	37	1	36	1.2	8.0	28	0.01
KL18-07	192	195	1.18		11800	1.01	2.2	98	0.01	140	29	0.01	37	0.8	7.5	20	0.01
KL18-07	195	198	2.37		23700	1.72	3	139	0.01	67	225	0.01	50	0.5	13.5	35	0.01
KL18-07	198	201	2.58		25800	2.05	3.4	171	0.01	30	311	0.01	51	0.3	16.9	34	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL18-07	201	204	3.71	37100	2.74	3.8	197	0.01	20	100	0.01	35	0.3	12.0	30	0.01
KL18-07	204	207	3.7	37000	2.86	6.5	214	0.01	6	94	0.01	37	0.01	7.5	78	0.01
KL18-07	207	210	3.97	39700	2.28	6.5	213	0.01	8	262	0.01	33	0.01	6.3	100	0.01
KL18-07	210	213	1.88	18800	1.66	2.9	148	0.01	10	115	0.01	41	0.01	39.0	89	0.01
KL18-07	213	216	1.58	15800	1.59	1.3	124	0.01	14	224	1	20	0.01	11.0	107	0.01
KL18-07	216	219	0.51	5100	0.34	0.8	41	0.01	22	72	1	6	0.8	3.9	83	0.01
KL18-07	219	222	0.73	7300	0.47	0.9	68	0.01	9	127	0.01	14	0.4	4.8	87	0.01
KL18-07	222	225	0.3	3000	0.17	0.01	62	7	8	267	0.01	14	0.6	9.8	61	0.01
KL18-07	225	228	0.73	7300	0.71	0.01	74	5	3	20	1	16	0.01	11.0	128	0.01
KL18-07	228	231	1.44	14400	1.21	1.8	83	0.01	0.01	76	0.01	21	0.01	8.0	158	0.01
KL18-07	231	233.5	0.84	8400	0.51	1	57	0.01	0.01	167	0.01	18	0.01	6.0	107	0.01
KL18-07	233.5	235.5	1.47	14700	0.45	6.9	1000	440	420	132	62	17	12.7	11.0	80	0.1
KL18-07	235.5	238.5	1.5	15000	0.36	7.1	1230	640	530	230	46	13	9.8	4.0	71	0.21
KL18-07	238.5	241.5	1.23	12300	1.6	1.3	70	14	27	460	2	13	0.2	6.5	132	0.01
KL18-07	241.5	244.5	1.72	17200	2.3	2.9	58	6	28	226	3	15	1.1	8.3	135	0.01
KL18-07	244.5	247.5	1.32	13200	1.08	2.2	75	24	44	210	2	11	3.6	3.3	175	0.01
KL18-07	247.5	250.5	1.45	14500	1.1	2.6	106	65	100	248	2	14	5	2.5	124	0.01
KL18-07	250.5	253.5	1.52	15200	0.75	6	374	111	34	123	1	29	2.8	6.0	121	0.01
KL18-07	253.5	256.5	1.61	16100	1.13	7.1	93	21	30	410	1	16	2.1	7.0	91	0.01
KL18-07	256.5	259.5	1.07	10700	1.53	1.1	55	5	3	42	1	11	0.3	4.5	147	0.01
KL18-07	259.5	262.5	0.72	7200	0.53	3.4	640	500	28	80	3	10	5.5	5.0	132	0.01
KL18-07	262.5	265.5	1.19	11900	1.62	1.1	78	5	8	97	2	18	1	6.4	147	0.01
KL18-07	265.5	268.5	0.99	9900	1.4	0.7	58	0.01	2	89	0.01	14	0.3	4.5	122	0.01
KL18-07	268.5	271.5	0.77	7700	0.69	0.5	62	0.01	2	253	1	13	0.4	4.8	114	0.01
KL18-07	271.5	274.5	0.89	8900	0.92	0.7	75	9	2	182	1	17	0.2	3.0	73	0.01
KL18-07	274.5	275.5	1.7	17000	1.62	1.2	84	18	4	1250	1	18	0.2	4.5	72	0.01
KL18-07	275.5	280.5	1.09	10900	0.72	0.6	73	11	2	140	0.01	17	0.2	6.5	61	0.01
KL18-07	280.5	286.5	0.93	9300	1.09	0.01	63	8	2	40	1	14	0.2	5.8	64	0.01
KL18-07	286.5	292	0.73	7300	0.63	0.6	72	60	9	57	1	13	0.5	5.5	70	0.01
KL18-07	292	295.5	1.6	16000	0.84	1.4	106	22	10	135	1	18	0.7	5.0	70	0.01
KL18-07	295.5	299.5	1.4	14000	1.52	5.6	550	187	35	127	2	16	9.7	3.0	78	0.1
KL18-07	299.5	303	0.64	6400	0.4	0.6	96	17	5	100	2	10	0.2	4.5	77	0.01
KL18-07	303	305	0.74	7400	1.31	0.5	79	5	6	85	2	14	1.1	4.5	75	0.01
KL18-07	305	308	0.64	6400	0.54	0.01	67	0.01	4	30	1	15	0.4	3.8	73	0.01
KL18-07	308	310.5	0.53	5300	0.38	0.01	54	0.01	7	28	1	9	0.6	4.3	70	0.01
KL18-07	310.5	314	1.07	10700	0.75	0.7	64	0.01	6	60	1	17	0.5	4.8	76	0.01
KL18-07	314	317	1.2	12000	1.09	0.8	58	5	7	120	2	13	0.5	6.0	78	0.01
KL18-07	317	320	1.2	12000	1.25	0.7	66	6	7	45	2	14	0.01	5.5	77	0.01
KL18-07	320	322.5	1.21	12100	0.67	0.7	65	12	4	83	2	17	0.3	4.5	68	0.01
KL18-07	322.5	325.3	1.23	12300	0.72	0.8	116	39	6	275	1	25	0.3	4.5	70	0.01
KL18-07	325.3	328.5	1.7	17000	1.4	0.9	141	27	16	80	2	20	0.4	5.0	59	0.01
KL18-07	328.5	331.5	1.01	10100	0.76	1.1	114	36	11	75	1	15	1.3	5.3	61	0.01
KL18-07	331.5	334.5	0.83	8300	0.77	1	104	20	10	102	2	13	0.7	7.5	68	0.01
KL18-07	334.5	337.5	0.97	9700	0.88	3.3	530	315	110	45	1	13	3.9	7.3	76	0.01
KL18-07	337.5	340.5	0.93	9300	0.68	4	1010	480	180	30	2	10	12.3	6.5	58	0.01
KL18-07	340.5	345	1.16	11600	0.88	3.5	630	238	120	25	2	16	8.8	7.3	59	0.01
KL18-07	345	347.7	1.44	14400	1.29	3.2	204	16	8	14	1	24	1.2	10.7	60	0.01
KL18-07	347.7	350	0.57	5700	0.68	0.5	137	19	7	15	2	16	1	6.5	75	0.01
KL18-07	350	353	0.57	5700	0.67	0.01	146	12	5	18	2	15	1.1	6.0	71	0.01
KL18-07	353	356.5	1.05	10500	1.52	2.5	130	21	4	4	1	11	0.01	3.3	10	0.01
KL18-07	356.5	360	0.33	3300	0.43	1.2	377	193	31	83	1	4	2.8	3.5	33	0.01
KL18-07	360	363.6	0.315	3150	0.34	1	69	22	5	53	1	5	0.7	3.5	150	0.01
KL18-07	363.6	367	0.33	3300	0.3	1.1	128	49	7	13	1	4	0.8	2.3	112	0.01
KL18-07	367	370	0.39	3900	0.43	1.1	120	65	4	15	1	7	0.4	3.4	120	0.01
KL18-07	370	373	0.32	3200	0.25	0.8	136	103	3	10	1	6	0.01	2.5	187	0.01
KL18-07	373	376	0.43	4300	0.41	1.2	349	133	5	17	1	6	1.1	1.0	171	0.01
KL18-07	376	380	0.52	5200	0.53	1	114	34	6	8	1	7	0.4	3.0	141	0.01
KL18-07	380	383	0.58	5800	0.62	1.2	122	16	4	7	1	7	0.5	3.0	112	0.01
KL18-07	383	387	0.62	6200	0.75	1.7	308	73	20	10	2	7	1.5	4.0	112	0.01
KL18-07	387	392.9	0.27	2700	0.09	1.3	252	57	65	3	2	6	2	0.8	50	0.01
KL18-07	392.9	397.5	0.5	5000	0.35	0.9	76	16	26	10	0.01	8	0.6	3.2	66	0.01
KL18-07	397.5	401.3	0.45	4500	0.25	1	90	32	35	5	1	5	1.7	0.0	75	0.01
KL18-07	401.3	404.5	0.51	5100	0.38	0.9	59	17	17	14	0.01	8	0.6	0.0	80	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL18-08	198	201														
KL18-08	201	204														
KL18-08	204	207														
KL18-08	207	210														
KL18-08	210	213														
KL18-08	213	216														
KL18-08	216	219														
KL18-08	219	222														
KL18-08	222	225.1														
KL18-08	225.1	237														
KL18-08	237	247														
KL18-08	247	252														
KL18-08	252	255														
KL18-08	255	257														
KL18-08	257	260														
KL18-08	260	263.5														
KL18-08	263.5	266.5														
KL18-08	266.5	270														
KL18-08	270	273														
KL18-08	273	276														
KL18-08	276	277.5														
KL18-08	277.5	279.7														
KL18-08	279.7	282.6														
KL18-08	282.6	285.1														
KL18-08	285.1	289														
KL18-08	289	292.5														
KL18-08	292.5	295.5														
KL18-08	295.5	298.5														
KL18-08	298.5	301.5														
KL18-08	301.5	304.6														
KL18-08	304.6	307.5														
KL18-08	307.5	310.2														
KL18-08	310.2	313.5														
KL18-08	313.5	316.5														
KL18-08	316.5	319.5														
KL18-08	319.5	322.5														
KL18-08	322.5	325.5														
KL18-08	325.5	328.5														
KL18-08	328.5	331.5														
KL18-08	331.5	334.5														
KL18-08	334.5	337.5														
KL18-08	337.5	340.5														
KL18-08	340.5	343.5														
KL18-08	343.5	346.5														
KL18-08	346.5	349														
KL18-08	349	351.3														
KL18-08	351.3	356.2														
KL18-08	356.2	359.9														
KL18-08	359.9	364.4														
KL18-08	364.4	369.9														
KL18-08	369.9	378.7														
KL18-08	378.7	381.7														
KL18-08	381.7	384.7														
KL18-08	384.7	388														
KL18-08	388	392.5														
KL18-08	392.5	398.2														
KL18-08	398.2	402.7														
KL18-08	402.7	410.2														
KL18-08	410.2	413.9	0.191	1910	0.12	0.01	29	8	3	3	0.01	6	0.01	4.0	49	0.01
KL18-08	413.9	417.5	0.132	1320	0.2	0.01	38	9	3	5	0.01	5	0.01	1.9	40	0.01
KL18-08	417.5	422.5	0.337	3370	0.17	0.01	64	14	5	32	0.01	11	0.7	4.8	69	0.01
KL18-08	422.5	430.7	0.92	9200	0.6	1.5	94	15	9	12	0.01	11	1	5.7	64	0.01
KL18-08	430.7	434	1.07	10700	0.62	1.4	90	16	10	28	0.01	9	1.5	6.0	59	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL18-08	434	437.5	0.77	7700	0.4	1.6	82	14	12	66	1	11	0.7	8.0	63	0.01
KL18-08	437.5	443.2	0.81	8100	0.51	1.8	84	13	7	25	1	18	0.6	9.3	76	0.01
KL18-08	443.2	447.1	0.73	7300	0.71	1.5	69	9	4	22	1	15	0.2	8.8	68	0.01
KL18-08	447.1	452	1.01	10100	0.93	4.5	650	143	59	23	1	22	5.2	16.0	55	0.01
KL18-08	452	455.2	0.77	7700	0.75	2	212	42	240	50	1	23	18	9.8	62	0.52
KL18-08	455.2	458	0.98	9800	0.64	2.3	307	60	97	10	0.01	39	7.5	13.0	61	0.13
KL18-08	458	461.5	0.95	9500	0.48	1.9	352	79	4	36	0.01	59	0.2	17.0	56	0.01
KL18-08	461.5	467.5	1.35	13500	1.31	2	128	16	4	39	0.01	49	0.6	18.0	51	0.01
KL18-08	467.5	470.6	1.74	17400	1.8	2.5	90	15	13	75	6	23	0.7	29.5	69	0.01
KL18-08	470.6	473.5	0.63	6300	0.76	1.1	23	10	13	34	2	5	0.5	6.8	89	0.01
KL18-08	473.5	476.5	1.04	10400	1.26	2.1	60	26	86	32	3	6	2	9.0	86	0.01
KL18-08	476.5	480.7	0.66	6600	0.74	1.1	42	26	48	54	2	4	1.4	6.8	78	0.01
KL18-08	480.7	483.7	0.51	5100	0.59	0.9	106	15	110	37	1	5	1.2	5.5	88	0.01
KL18-08	483.7	486.7	0.48	4800	0.62	0.9	28	6	3	19	1	5	0.2	5.3	140	0.01
KL18-08	486.7	489.7	0.433	4330	0.43	1	101	10	8	38	1	9	0.01	5.9	113	0.01
KL18-08	489.7	492.7	0.57	5700	0.79	1	21	7	8	27	2	5	0.2	8.3	118	0.01
KL18-08	492.7	495.7	0.425	4250	0.61	0.7	22	11	3	40	1	4	0.01	5.3	106	0.01
KL18-08	495.7	498.7	0.54	5400	0.39	1	12	8	6	35	1	3	0.2	4.8	99	0.01
KL18-08	498.7	501.7	0.66	6600	0.87	1	28	10	8	35	2	7	1	8.5	163	0.01
KL18-08	501.7	504.7	0.55	5500	1.08	0.8	29	9	21	25	1	6	0.01	6.3	109	0.01
KL18-08	504.7	507.7	0.78	7800	0.69	0.9	23	10	3	26	2	8	0.3	6.0	85	0.01
KL18-08	507.7	510.7	0.69	6900	1.04	1	37	6	2	23	1	9	0.01	6.8	104	0.01
KL18-08	510.7	513.7	0.72	7200	0.58	1	42	7	3	27	0.01	9	0.2	7.0	143	0.01
KL18-08	513.7	516.7	0.5	5000	0.37	0.8	44	7	4	15	1	9	0.2	6.0	140	0.01
KL18-08	516.7	519.7	0.62	6200	0.63	0.8	38	6	3	9	0.01	6	0.01	5.0	158	0.01
KL18-08	519.7	522.7	0.503	5030	0.55	0.01	22	8	3	15	1	6	0.2	6.0	163	0.01
KL18-08	522.7	525.7	0.325	3250	0.36	0.6	23	6	6	9	0.01	4	0.3	2.0	109	0.01
KL18-09	0	5.2	0.0057	57	0.01	0.01	99	101	6	14	0.01	0.01	0.3	1.3	26	0.01
KL18-09	5.2	7.2	0.0044	44	0.01	0.01	69	80	3	5	0.01	0.01	0.01	0.8	26	0.01
KL18-09	7.2	10.2	0.0055	55	0.01	0.5	258	410	5	55	0.01	0.01	0.01	3.6	17	0.01
KL18-09	10.2	13.2	0.0037	37	0.05	1.9	403	860	20	20	3	0.01	0.4	7.2	20	0.01
KL18-09	13.2	16.2	0.0065	65	0.28	3	359	407	230	17	0.01	0.01	1	13.6	27	0.1
KL18-09	16.2	19.2	0.0014	14	0.01	0.5	263	244	7	10	0.01	0.01	0.4	2.8	18	0.01
KL18-09	19.2	22.2	0.0021	21	0.01	0.01	228	116	5	29	0.01	0.01	0.01	1.6	16	0.01
KL18-09	22.2	25.2	0.0022	22	0.01	0.01	211	409	5	40	0.01	0.01	0.3	3.1	18	0.01
KL18-09	25.2	28.2	0.0023	23	0.01	0.01	207	490	5	22	2	0.01	0.01	2.8	19	0.01
KL18-09	28.2	31.2	0.0018	18	0.02	2	123	234	8	8	5	0.01	0.3	2.8	24	0.01
KL18-09	31.2	34.2	0.0012	12	0.01	0.01	130	116	5	15	0.01	0.01	0.01	1.8	20	0.01
KL18-09	34.2	37.2	0.0011	11	0.03	1.5	245	400	6	22	8	0.01	0.01	5.3	21	0.01
KL18-09	37.2	40.2	0.002	20	0.01	0.01	193	770	3	22	0.01	0.01	0.6	3.2	13	0.01
KL18-09	40.2	43.2	0.0013	13	0.01	0.01	209	239	0.01	13	0.01	0.01	0.01	1.6	16	0.01
KL18-09	43.2	46.2	0.0008	8	0.01	0.01	155	200	1	20	0.01	0.01	0.2	1.2	23	0.01
KL18-09	46.2	49.2	0.0013	13	0.01	0.7	284	1000	3	20	0.01	0.01	0.5	2.3	19	0.01
KL18-09	49.2	52.5	0.001	10	0.01	0.01	140	242	1	25	0.01	0.01	0.01	1.3	16	0.01
KL18-09	52.5	55.5	0.0027	27	0.03	0.01	208	620	5	26	0.01	0.01	0.4	2.0	15	0.01
KL18-09	55.5	60.7	0.0023	23	0.05	0.01	250	391	10	16	0.01	0.01	0.01	2.0	16	0.01
KL18-09	60.7	63.8	0.003	30	0.02	0.01	331	810	5	13	0.01	0.01	0.3	2.4	18	0.01
KL18-09	63.8	67.2	0.0036	36	0.07	0.01	520	650	6	8	1	0.01	0.4	3.0	18	0.01
KL18-09	67.2	70.2	0.0054	54	0.05	0.6	1080	1220	12	10	0.01	0.01	0.6	4.6	11	0.01
KL18-09	70.2	73.2	0.0115	115	0.03	2.1	392	2450	14	18	3	0.01	1.5	3.2	21	0.01
KL18-09	73.2	76.2	0.0123	123	0.02	2.3	440	570	17	16	12	0.01	0.6	3.3	40	0.01
KL18-09	76.2	79.2	0.0066	66	0.01	0.7	387	244	10	5	6	0.01	0.01	2.3	18	0.01
KL18-09	79.2	82.2	0.0076	76	0.04	1.1	570	365	10	12	11	0.01	0.01	1.6	27	0.01
KL18-09	82.2	89.2	0.0142	142	0.02	1.1	720	480	16	4	10	2	0.6	2.6	16	0.01
KL18-09	89.2	96.7	0.0132	132	0.01	1.2	610	241	14	6	15	0.01	0.3	2.0	18	0.01
KL18-09	96.7	101.2	0.0079	79	0.01	0.01	352	37	14	4	2	0.01	0.2	1.1	18	0.01
KL18-09	101.2	104.2	0.0078	78	0.01	0.01	310	52	14	3	3	0.01	0.2	1.7	18	0.01
KL18-09	104.2	106.7	0.0064	64	0.01	0.01	230	69	10	8	4	0.01	0.01	1.0	21	0.01
KL18-09	106.7	110.2	0.009	90	0.02	0.6	570	372	11	13	5	0.01	0.3	2.8	28	0.01
KL18-09	110.2	116.2	0.012	120	0.01	1.8	403	460	24	4	8	0.01	0.4	4.9	17	0.01
KL18-09	116.2	128.2	0.0107	107	0.01	0.6	193	103	14	3	4	0.01	0.3	1.4	21	0.01
KL18-09	128.2	132.8	0.0137	137	0.01	0.6	198	137	11	2	3	0.01	0.01	0.8	21	0.01
KL18-09	132.8	137.2	0.004	40	0.01	2.1	710	1330	10	3	5	0.01	1.5	1.3	17	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL18-09	137.2	146.2	0.0097		97	0.03	3.1	950	940	38	18	8	0.01	1.2	2.3	16	0.01
KL18-09	146.2	152.2	0.0062		62	0.01	0.6	116	185	16	4	3	2	0.3	1.1	18	0.01
KL18-09	152.2	162.8	0.0049		49	0.01	1.7	244	248	11	3	4	0.01	0.3	0.9	21	0.01
KL18-09	162.8	167.4	0.0047		47	0.01	2.5	205	372	8	4	7	0.01	0.2	0.8	20	0.01
KL18-09	167.4	170.4	0.0065		65	0.01	4.5	580	830	15	3	10	0.01	0.3	1.7	13	0.01
KL18-09	170.4	176.2	0.0039		39	0.01	0.8	143	205	6	14	3	0.01	0.01	2.0	17	0.01
KL18-09	176.2	182.2	0.0101		101	0.01	0.7	401	187	29	13	4	0.01	0.6	1.0	18	0.01
KL18-09	182.2	185.2	0.0058		58	0.01	0.5	229	179	13	8	2	0.01	0.01	1.4	20	0.01
KL18-09	185.2	188.2	0.004		40	0.01	0.8	179	349	9	76	1	0.01	0.4	1.5	18	0.01
KL18-09	188.2	192.7	0.0024		24	0.02	1.2	143	236	8	24	0.01	2	0.4	1.6	20	0.01
KL18-09	192.7	200.2	0.0026		26	0.02	1.2	420	330	5	20	1	2	0.6	1.1	20	0.01
KL18-09	200.2	215	0.0017		17	0.02	1.7	184	218	5	18	0.01	2	0.6	1.3	20	0.01
KL18-09	215	221.2	0.0024		24	0.06	2.2	156	157	10	18	0.01	2	0.7	1.8	20	0.01
KL18-09	221.2	227.2	0.0025		25	0.02	2.6	188	740	6	16	0.01	2	0.7	6.0	17	0.01
KL18-09	227.2	231.4	0.0016		16	0.02	1.3	135	226	7	12	0.01	2	0.6	1.5	18	0.01
KL18-09	231.4	234.7	0.0063		63	0.01	0.9	140	248	7	7	0.01	2	0.7	2.1	16	0.01
KL18-09	234.7	242.2	0.0058		58	0.01	1	89	175	6	6	0.01	3	0.4	0.7	18	0.01
KL18-09	242.2	248.2	0.0088		88	0.06	1.8	112	101	9	21	0.01	2	0.7	0.8	20	0.01
KL18-09	248.2	257.2	0.008		80	0.06	12.9	650	10500	19	22	0.01	2	10.5	9.0	18	0.01
KL18-09	257.2	262.7	0.0061		61	0.01	1.9	175	470	5	16	0.01	2	1	1.9	17	0.01
KL18-09	262.7	266.2	0.0097		97	0.01	1.4	107	268	7	19	0.01	2	0.7	2.3	20	0.01
KL18-09	266.2	269.2	0.0089		89	0.01	1.2	74	92	7	10	0.01	3	0.6	1.2	20	0.01
KL18-09	269.2	273.5	0.0088		88	0.01	3.4	119	201	8	7	0.01	2	0.7	3.0	16	0.01
KL18-09	273.5	279.2	0.0094		94	0.01	1.7	212	189	6	7	0.01	3	0.9	2.6	21	0.01
KL18-09	279.2	284.2	0.0176		176	0.01	0.9	109	190	3	6	0.01	3	0.6	1.6	18	0.01
KL18-09	284.2	289.6	0.0165		165	0.01	1.4	198	310	4	5	0.01	3	0.7	2.0	17	0.01
KL18-09	289.6	293.2	0.0161		161	0.01	1.5	226	520	7	9	0.01	3	1.2	2.3	16	0.01
KL18-09	293.2	297.6	0.0114		114	0.02	2.1	410	690	8	26	0.01	4	1.4	8.1	24	0.01
KL18-09	297.6	301.7	0.0072		72	0.06	11.2	2620	2700	23	21	0.01	2	4.6	9.6	22	0.15
KL18-09	301.7	305.2	0.0042		42	0.02	5.8	1490	1040	5	12	0.01	0.01	2.6	4.6	12	0.1
KL18-09	305.2	311.2	0.0097		97	0.02	1.6	209	255	4	17	0.01	0.01	0.7	3.3	20	0.01
KL18-09	311.2	316.4	0.0094		94	0.02	1.7	281	460	6	15	0.01	0.01	1.2	7.1	18	0.01
KL18-09	316.4	322.7	0.0155		155	0.02	0.9	137	295	6	27	0.01	0.01	0.6	2.8	16	0.01
KL18-09	322.7	327.6	0.0118		118	0.01	2.8	194	640	10	37	0.01	0.01	1	4.7	18	0.01
KL18-09	327.6	330.7	0.013		130	0.01	0.8	141	248	7	13	0.01	0.01	0.7	1.6	16	0.01
KL18-09	330.7	333.7	0.0148		148	0.07	4.6	760	1420	18	45	1	2	2.2	10.5	21	0.01
KL18-09	333.7	338.5	0.0138		138	0.03	3.2	740	1280	16	24	0.01	2	1.8	8.9	17	0.01
KL18-09	338.5	344.2	0.0071		71	0.01	2	272	520	7	27	0.01	0.01	0.8	4.6	20	0.01
KL18-09	344.2	349.5	0.0095		95	0.02	3.2	273	304	8	36	0.01	0.01	0.5	2.6	20	0.01
KL18-09	349.5	353.7	0.0061		61	0.02	2.1	191	173	8	45	0.01	0.01	0.6	2.1	19	0.01
KL18-09	353.7	357.2	0.0076		76	0.01	1	169	410	16	17	0.01	0.01	0.7	4.6	20	0.01
KL18-09	357.2	361.1	0.007		70	0.02	1.1	207	450	47	26	0.01	2	0.8	4.3	26	0.01
KL18-09	361.1	364.2	0.0101		101	0.11	4	810	1490	46	22	0.01	0.01	2.5	12.3	25	0.01
KL18-09	364.2	366.5	0.008		80	0.15	4.3	700	1170	34	40	0.01	2	2.6	7.4	22	0.01
KL18-09	366.5	369.8	0.0102		102	0.07	4.6	1070	3020	140	20	1	2	9.6	10.6	19	0.01
KL18-09	369.8	372.5	0.0091		91	0.06	5.8	690	1770	160	45	1	2	6	10.0	20	0.01
KL18-09	372.5	377.2	0.018		180	0.13	52.3	1450	1170	58	29	1	3	1.8	6.7	18	0.12
KL18-09	377.2	383.2	0.0235		235	0.06	45.9	2940	2040	140	19	1	2	18.3	13.3	14	0.14
KL18-09	383.2	386.2	0.0097		97	0.1	35.8	1270	3250	170	12	0.01	2	12.4	26.3	12	0.01
KL18-09	386.2	392.2	0.0117		117	0.16	20.1	1420	1740	22	50	1	3	4.8	9.0	20	0.15
KL18-09	392.2	395.2	0.046		460	0.21	109.5	6000	4900	150	65	40	4	25	20.1	25	0.7
KL18-09	395.2	398.2	0.0096		96	0.16	23	720	900	31	19	2	3	4.2	7.3	27	0.01
KL18-09	398.2	401.2	0.0083		83	0.1	11.2	600	910	12	26	2	3	1.7	10.8	25	0.01
KL18-09	401.2	404.2	0.012		120	0.29	18.5	1290	1820	22	50	4	3	3	22.0	43	0.01
KL18-09	404.2	407.2	0.0084		84	0.14	8.8	1630	1050	31	22	2	5	1.7	27.0	29	0.01
KL18-09	407.2	411.7	0.0034		34	0.11	5.2	398	460	45	19	1	2	1.6	6.7	30	0.01
KL18-09	411.7	415.5	0.0097		97	0.13	4.3	363	302	29	15	2	3	1.8	5.3	26	0.01
KL18-09	415.5	419.2	0.043		430	0.34	12.8	1900	1390	150	56	14	4	5	20.0	47	0.15
KL18-09	419.2	425.2	0.0072		72	0.22	25.9	1480	840	32	20	1	2	2.8	24.0	40	0.1
KL18-09	425.2	426.7	0.0086		86	0.27	11.5	1890	1520	52	98	0.01	3	3.2	48.0	43	0.1
KL18-09	426.7	428.2	0.0118		118	2.83	28.1	1460	1190	420	58	4	13	28	75.0	141	0.41
KL18-09	428.2	431.2	0.019		190	7.37	52	7780	4350	970	98	5	15	64	123.0	155	0.33
KL18-10	0	6	0.148		1480	0.06	2.4	400	358	89	36	1	0.01	26	3.4	17	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL18-10	6	9	0.008		80	0.02	0.7	230	164	23	5	2	0.01	1	3.6	21	0.01
KL18-10	9	12	0.0079		79	0.05	0.5	118	71	17	24	3	0.01	0.9	3.2	23	0.01
KL18-10	12	14	0.043		430	0.55	80	14200	16300	32	25	9	0.01	9.8	380.0	22	0.01
KL18-10	14	17	0.0088		88	0.02	4.8	450	750	13	4	1	0.01	0.7	14.9	13	0.01
KL18-10	17	19.5	0.0203		203	0.08	4	1620	440	23	15	31	0.01	1.4	15.4	20	0.01
KL18-10	19.5	22.5	0.0216		216	0.05	1.6	480	263	11	7	9	0.01	1	6.8	24	0.01
KL18-10	22.5	25.5	0.0229		229	0.03	1.5	267	260	13	16	16	0.01	0.9	7.5	24	0.01
KL18-10	25.5	28.5	0.0273		273	0.09	1.7	370	306	21	7	13	0.01	0.6	7.1	19	0.01
KL18-10	28.5	31.5	0.0141		141	0.06	0.7	258	66	16	6	2	2	0.8	2.4	20	0.01
KL18-10	31.5	34.5	0.005		50	0.15	0.01	245	42	17	6	0.01	2	0.7	1.3	22	0.01
KL18-10	34.5	37.5	0.0354		354	0.11	1	358	176	8	23	4	4	1	5.2	42	0.01
KL18-10	37.5	40.5	0.111		1110	0.27	9.6	2960	2860	20	19	19	6	1.6	65.5	58	0.01
KL18-10	40.5	43.5	0.0069		69	0.08	0.01	310	57	15	7	5	0.01	0.2	3.0	23	0.01
KL18-10	43.5	46.5	0.0193		193	0.05	2.8	1100	1130	12	8	20	0.01	0.3	21.2	23	0.01
KL18-10	46.5	49.5	0.0069		69	0.01	1.4	490	610	15	6	10	0.01	0.7	11.6	20	0.01
KL18-10	49.5	52.5	0.0154		154	0.03	3.3	490	1000	15	6	21	0.01	0.5	44.0	21	0.01
KL18-10	52.5	55.5	0.056		560	0.07	1.6	262	220	19	131	7	6	0.6	6.4	81	0.01
KL18-10	55.5	58.5	0.0089		89	0.12	2	480	206	15	4	8	2	0.7	4.5	27	0.01
KL18-10	58.5	61.5	0.005		50	0.01	0.6	202	70	11	2	3	0.01	0.3	1.7	14	0.01
KL18-10	61.5	64.5	0.0223		223	0.02	1	375	145	13	3	4	2	0.3	4.5	21	0.01
KL18-10	64.5	66.7	0.041		410	0.02	1.8	630	224	12	6	5	2	0.8	4.7	22	0.01
KL18-10	66.7	69.1	0.0042		42	0.11	1.4	103	92	7	4	0.01	0.01	0.4	2.5	15	0.01
KL18-10	69.1	72	0.0212		212	0.05	7.1	1370	1650	17	9	14	0.01	0.7	41.8	30	0.01
KL18-10	72	75	0.0381		381	0.05	3.6	3030	2780	29	5	0.01	3	1.6	51.5	32	0.01
KL18-10	75	78	0.0289		289	0.06	4.9	4620	7500	18	4	3	3	1	52.5	26	0.01
KL18-10	78	81	0.0094		94	0.01	1.7	1050	1540	7	5	1	0.01	0.5	17.0	16	0.01
KL18-10	81	84	0.0073		73	0.04	1.9	590	650	8	3	1	3	0.6	11.1	20	0.01
KL18-10	84	87	0.0049		49	0.01	2.9	365	540	4	4	0.01	0.01	0.7	4.1	15	0.01
KL18-10	87	90	0.0038		38	0.01	1	332	500	4	2	0.01	0.01	0.6	3.8	12	0.01
KL18-10	90	93	0.0138		138	0.03	2.2	1180	2050	11	12	0.01	2	1.2	14.5	15	0.01
KL18-10	93	96	0.011		110	0.02	1.6	2380	3370	6	12	0.01	3	1.3	24.4	16	0.01
KL18-10	96	99	0.0063		63	0.04	2	950	1910	7	39	3	2	0.9	11.0	14	0.01
KL18-10	99	102	0.0148		148	0.04	8.6	4460	11000	13	22	3	3	4.1	46.0	16	0.01
KL18-10	102	105	0.0243		243	0.01	4.9	1480	4000	9	53	11	0.01	1.3	41.5	18	0.01
KL18-10	105	108	0.0196		196	0.01	3.5	1170	10400	28	23	0.01	0.01	2.6	43.3	16	0.01
KL18-10	108	111	0.0219		219	0.02	1.4	1150	1750	9	5	0.01	0.01	0.8	9.3	18	0.01
KL18-10	111	114	0.0247		247	0.01	6.3	1310	10500	13	40	0.01	0.01	5.8	28.5	15	0.01
KL18-10	114	117	0.0109		109	0.01	1.4	980	1310	10	5	0.01	0.01	1.5	7.6	16	0.01
KL18-10	117	120	0.041		410	0.01	1.7	1170	1550	15	30	0.01	2	1.7	13.2	16	0.01
KL18-10	120	123	0.0136		136	0.01	1.6	1130	1205	11	25	0.01	0.01	1.4	9.4	17	0.01
KL18-10	123	126	0.0051		51	0.01	1.3	377	530	5	5	0.01	0.01	0.9	3.9	11	0.01
KL18-10	126	127.6	0.0067		67	0.01	0.9	395	372	9	5	0.01	0.01	0.9	2.7	9	0.01
KL18-10	127.6	130.5	0.0141		141	0.03	1.2	560	750	5	6	15	0.01	0.7	12.5	13	0.01
KL18-10	130.5	133.5	0.125		1250	0.14	3.8	16700	19300	23	60	59	3	2.1	180.0	34	0.01
KL18-10	133.5	136.5	0.134		1340	0.07	12.8	15000	23400	12	60	10	2	3	175.0	17	0.01
KL18-10	136.5	139.5	0.24		2400	0.23	29.6	36500	54100	350	133	2	3	19.1	275.0	25	0.01
KL18-10	139.5	142.5	0.086		860	0.02	40	3810	7500	44	79	0.01	0.01	2.5	28.0	14	0.01
KL18-10	142.5	145.5	0.0409		409	0.18	27.4	24300	26800	25	98	0.01	0.01	7.9	53.5	17	0.1
KL18-10	145.5	148.5	0.064		640	0.22	35.3	28000	27400	230	56	4	0.01	16.2	48.5	21	0.47
KL18-10	148.5	151.5	0.088		880	0.13	13.5	25600	21000	250	55	4	0.01	12.6	30.0	22	0.17
KL18-10	151.5	154.5	0.0108		108	0.01	2.7	1940	1920	15	23	0.01	0.01	1.7	8.3	11	0.01
KL18-10	154.5	157.5	0.041		410	0.01	6.6	8100	8200	15	12	0.01	0.01	3.9	10.0	16	0.01
KL18-10	157.5	160.5	0.083		830	0.04	16.6	14500	21800	7	16	0.01	0.01	5.5	143.0	17	0.01
KL18-10	160.5	163.5	0.0157		157	0.03	2	2770	2480	16	4	0.01	0.01	1.2	13.0	16	0.01
KL18-10	163.5	166.5	0.0178		178	0.08	3.5	5100	3060	17	6	1	2	2.6	14.1	17	0.01
KL18-10	166.5	169.5	0.0138		138	0.05	1.8	3200	1920	20	3	0.01	0.01	1.9	5.5	21	0.01
KL18-10	169.5	172.5	0.045		450	0.19	5.6	7300	5200	42	37	3	3	4.7	25.5	19	0.1
KL18-10	172.5	175.5	0.0123		123	0.06	1.7	1910	1375	17	0.01	0.01	0.01	1.3	10.7	14	0.01
KL18-10	175.5	178.5	0.0145		145	0.07	1.3	460	550	9	4	0.01	4	0.8	8.6	18	0.01
KL18-10	178.5	181.5	0.123		1230	0.15	57.3	9400	67000	39	32	114	4	14.8	410.0	24	0.01
KL18-10	181.5	184.5	0.153		1530	0.11	29.3	3360	14000	20	35	710	15	4.4	132.0	15	0.01
KL18-10	184.5	187.5	0.62		6200	0.1	15.6	10400	2800	48	650	163	20	4.2	68.5	35	0.01
KL18-10	187.5	193.5	0.0283		283	0.06	3.7	3780	1560	46	960	11	0.01	5.4	11.2	39	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL18-10	193.5	196.5	0.071	710	0.02	2	1480	490	12	1490	11	0.01	1	13.1	53	0.01
KL18-10	196.5	199.5	0.0255	255	0.04	2.5	2400	1850	22	450	9	0.01	3.6	9.1	88	0.01
KL18-10	199.5	202.5	0.0245	245	0.05	2.8	3570	800	16	123	4	0.01	1.7	7.4	37	0.01
KL18-10	202.5	205	0.0278	278	0.02	3.7	2930	490	18	75	26	2	0.6	7.5	43	0.01
KL18-10	205	208.2	0.058	580	0.04	2.1	11200	189	9	74	160	5	0.01	11.2	34	0.01
KL18-10	208.2	211.4	0.0304	304	0.28	2.5	1880	490	15	600	29	0.01	0.7	6.8	40	0.01
KL18-10	211.4	214.5	0.089	890	0.24	6.8	2910	1150	350	66	28	0.01	14.2	20.2	60	0.01
KL18-10	214.5	217.5	0.0108	108	0.01	0.5	282	118	10	910	1	0.01	0.7	3.1	57	0.01
KL18-10	217.5	220.6	0.0078	78	0.06	1.2	810	450	11	1010	2	0.01	0.3	5.3	88	0.01
KL18-10	220.6	223.5	0.0217	217	0.14	4	2560	910	38	450	13	2	3	9.2	89	0.01
KL18-10	223.5	226.5	0.35	3500	0.04	3	5000	261	17	121	75	11	1.3	11.9	47	0.01
KL18-10	226.5	229.5	0.0165	165	0.01	1	470	135	10	910	5	2	0.7	3.9	34	0.01
KL18-10	229.5	232.5	0.0133	133	0.01	0.5	920	136	6	980	3	4	0.8	4.9	38	0.01
KL18-10	232.5	235.5	0.071	710	0.33	3	4910	58	19	13	2	17	2.1	6.4	9	0.01
KL18-10	235.5	238.5	0.289	2890	0.36	1.5	1880	64	19	26	4	15	1.1	10.3	33	0.01
KL18-10	238.5	241.5	0.173	1730	0.15	1.1	6200	100	14	78	6	14	0.9	6.9	12	0.01
KL18-10	241.5	244.5	0.76	7600	0.52	5.9	450	224	22	440	110	17	0.8	7.3	7	0.01
KL18-10	244.5	247.5	0.51	5100	0.55	2.3	6700	100	20	155	13	13	1.4	7.2	27	0.01
KL18-10	247.5	250.5	0.27	2700	0.18	1.5	152	19	7	530	8	3	1.1	4.4	44	0.01
KL18-10	250.5	253.5	0.44	4400	0.4	2.5	1380	19	16	465	7	10	0.2	0.0	66	0.01
KL18-10	253.5	256.5	0.75	7500	2.1	1.8	950	19	34	230	10	20	0.4	8.2	18	0.01
KL18-10	256.5	259.5	1.32	13200	1.53	3	490	27	18	135	7	15	0.2	10.2	49	0.01
KL18-10	259.5	262.5	0.354	3540	0.66	1.5	210	14	8	269	2	14	0.01	5.4	79	0.01
KL18-10	262.5	265.5	0.417	4170	0.39	1.2	120	13	14	310	1	6	0.01	4.8	49	0.01
KL18-10	265.5	268.5	1.01	10100	0.55	7.5	14700	201	130	78	2	43	9.3	10.8	35	0.01
KL18-10	268.5	271.5	0.371	3710	0.32	2.5	1100	202	33	403	3	21	7.3	8.1	113	0.01
KL18-10	271.5	274.5	0.67	6700	0.63	2.2	1100	24	19	258	62	26	0.8	8.1	51	0.01
KL18-10	274.5	277.5	1.57	15700	1.65	1.7	19200	11	30	440	47	51	0.2	18.5	58	0.01
KL18-10	277.5	280.5	1.35	13500	1.18	2.9	3600	31	12	234	4	32	0.01	17.0	14	0.01
KL18-10	280.5	283.5	0.78	7800	0.93	2.2	850	27	11	118	2	15	0.01	7.6	34	0.01
KL18-10	283.5	286.5	0.314	3140	0.3	1.9	1540	210	120	271	8	9	2.2	8.6	80	0.01
KL18-10	286.5	291.7	0.454	4540	0.43	1.8	220	59	33	100	4	10	1.2	7.9	76	0.01
KL18-10	291.7	294.5	0.74	7400	0.93	2.7	170	34	22	980	12	11	2.1	14.2	54	0.01
KL18-10	294.5	298.5	0.99	9900	1.03	2.7	510	88	48	410	4	18	4.7	11.0	41	0.01
KL18-10	298.5	303.5	1.18	11800	0.66	3.3	410	29	26	311	5	15	1.6	15.5	40	0.01
KL18-10	303.5	306	2.32	23200	2.12	3.7	50800	86	39	116	4	131	1.4	64.0	50	0.01
KL18-10	306	309.5	1.19	11900	2.24	3.1	48000	30	26	188	3	37	1.1	16.0	44	0.01
KL18-10	309.5	312	0.363	3630	0.49	1.3	175	15	16	403	2	8	1.2	5.5	61	0.01
KL18-10	312	315	0.478	4780	0.48	1.5	161	12	23	490	2	14	1.4	4.6	32	0.01
KL18-10	315	317.5	1.44	14400	2.22	3.6	244	22	38	650	5	15	1.6	15.5	42	0.01
KL18-10	317.5	319.8	2.02	20200	4.18	7	390	36	40	128	40	59	1.3	19.8	35	0.01
KL18-10	319.8	323.3	0.72	7200	1.56	1.5	140	16	89	430	6	6	1.2	5.8	119	0.01
KL18-10	323.3	325.7	0.71	7100	1.37	1.5	110	15	91	440	5	9	1.2	7.4	123	0.01
KL18-10	325.7	328.5	1.35	13500	4.01	2.4	140	6	14	520	5	15	0.4	11.0	66	0.01
KL18-10	328.5	330.7	0.378	3780	1.61	1	65	8	17	2200	3	6	0.2	6.3	69	0.01
KL18-10	330.7	333.7	0.294	2940	0.24	1.1	147	41	88	710	2	6	3.1	4.0	114	0.01
KL18-10	333.7	336	0.227	2270	0.38	0.9	97	26	52	880	2	6	0.8	5.0	105	0.01
KL18-10	336	340.5	0.15	1500	0.14	0.8	88	16	24	367	1	8	0.6	4.0	82	0.01
KL18-10	340.5	343.5	0.92	9200	0.88	2.2	317	8	19	260	1	48	0.4	5.8	68	0.01
KL18-10	343.5	346.5	0.213	2130	0.29	0.01	70	5	14	52	0.01	11	0.01	3.4	43	0.01
KL18-10	346.5	349.5	0.254	2540	0.31	0.6	102	5	13	142	0.01	13	0.01	3.3	55	0.01
KL18-10	349.5	352.5	0.6	6000	0.67	0.9	235	0.01	16	89	0.01	22	1.1	4.9	36	0.01
KL18-10	352.5	355.5	0.441	4410	0.51	0.9	160	6	13	167	0.01	24	0.8	5.1	57	0.01
KL18-10	355.5	358.5	0.74	7400	1.2	1.5	150	5	3	36	0.01	30	0.2	8.4	38	0.01
KL18-10	358.5	361.5	1.52	15200	2.9	3	170	11	8	189	0.01	40	0.4	16.0	49	0.01
KL18-10	361.5	364	0.35	3500	0.36	1.2	170	84	4	33	0.01	25	0.3	4.8	69	0.01
KL18-10	364	367	1.02	10200	2.13	5.8	780	660	28	102	7	24	0.9	13.3	30	0.01
KL18-10	367	370	0.7	7000	0.78	3.2	237	74	21	324	5	16	0.6	9.5	36	0.01
KL18-10	370	373	2.11	21100	3.72	6.9	600	218	12	146	2	71	0.5	9.8	75	0.01
KL18-10	373	376	0.61	6100	1.03	1.5	72	47	4	270	0.01	12	0.2	7.0	38	0.01
KL18-10	376	379	1.7	17000	2.66	4.1	305	30	3	306	0.01	32	0.3	13.0	36	0.01
KL18-10	379	382	2.88	28800	2.78	5	1070	48	6	15	1	84	0.4	10.0	54	0.01
KL18-10	382	384.4	2.13	21300	6.1	7.6	420	34	6	204	1	50	0.3	9.0	34	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL18-10	384.4	387.4	1.76	17600	1.84	3.6	272	22	10	24	1	37	0.7	18.5	40	0.01
KL18-10	387.4	390.4	1.4	14000	0.84	2.8	155	13	9	34	1	36	0.9	16.8	120	0.01
KL18-10	390.4	393.4	1.6	16000	1.44	1.6	113	13	5	40	1	24	0.4	14.0	73	0.01
KL18-10	393.4	396.4	1.34	13400	1.86	1.1	55	12	1	6	2	11	0.01	13.0	70	0.01
KL18-10	396.4	399.4	3.63	36300	2.72	13.6	71	26	470	11	8	14	18	13.0	86	0.01
KL18-10	399.4	402.4	0.83	8300	0.68	1.5	44	18	360	2	4	18	20	31.4	41	0.01
KL18-10	402.4	405.4	1.71	17100	0.62	1.2	50	22	31	20	0.01	20	2.2	12.0	90	0.01
KL18-10	405.4	408.4	2.43	24300	2.18	2.1	52	25	8	53	5	15	1.4	16.0	43	0.01
KL18-10	408.4	411.4	1.89	18900	2.34	2.3	85	9	2	299	4	5	0.2	8.5	116	0.01
KL18-10	411.4	414.4	1.21	12100	1.71	1.8	54	15	2	42	3	9	0.4	8.5	102	0.01
KL18-10	414.4	417.4	1.05	10500	2.89	2	67	14	0.01	37	2	11	0.7	8.3	113	0.01
KL18-10	417.4	420.4	1.61	16100	3.04	2.8	40	16	0.01	52	8	10	0.5	12.8	69	0.01
KL18-10	420.4	423.4	0.98	9800	1.03	2.4	34	18	14	24	4	8	1.5	6.3	53	0.01
KL18-10	423.4	426.4	0.8	8000	1.88	1.5	60	9	3	56	1	11	0.7	5.8	120	0.01
KL18-10	426.4	429.4	1.05	10500	2.58	2.1	38	7	1	104	3	8	0.01	5.0	126	0.01
KL18-10	429.4	432.4	0.92	9200	0.57	1.6	72	8	1	58	0.01	15	0.01	5.8	67	0.01
KL18-10	432.4	435.4	0.85	8500	1.78	2	47	10	8	86	4	6	0.6	4.3	67	0.01
KL18-10	435.4	438.4	1.1	11000	1.42	1.6	67	13	0.01	36	2	13	0.01	6.1	70	0.01
KL18-10	438.4	441.4	0.64	6400	1	1.2	50	14	0.01	41	1	7	0.01	5.0	79	0.01
KL18-10	441.4	444.4	0.82	8200	1.07	1.5	75	15	1	25	1	10	0.2	6.0	86	0.01
KL18-10	444.4	447.4	0.65	6500	1.13	1.7	55	9	2	48	1	8	0.01	5.4	138	0.01
KL18-10	447.4	450.4	0.91	9100	0.73	1.2	71	15	3	37	1	14	0.4	6.5	112	0.01
KL18-10	450.4	453	0.66	6600	0.52	1.3	88	16	5	31	1	10	2.1	5.5	71	0.01
KL18-10	453	456	0.54	5400	0.55	1	71	5	1	34	0.01	7	0.01	4.5	63	0.01
KL18-10	456	459	0.56	5600	0.86	1.1	43	6	0.01	26	1	6	0.01	3.8	67	0.01
KL18-10	459	462	0.55	5500	0.89	0.9	40	8	0.01	23	1	5	0.01	3.5	72	0.01
KL18-10	462	465	0.74	7400	1.06	1.5	50	9	7	29	2	7	1.1	5.8	111	0.01
KL18-10	465	468	0.57	5700	0.48	1	63	16	3	52	0.01	10	0.2	8.5	62	0.01
KL18-10	468	471	0.436	4360	0.41	1.2	84	15	2	75	0.01	12	0.3	6.4	112	0.01
KL18-10	471	474	0.44	4400	0.39	1.4	57	14	2	24	0.01	10	0.01	7.3	60	0.01
KL18-10	474	477	0.59	5900	0.67	1	62	9	4	19	1	9	0.01	5.0	103	0.01
KL18-10	477	480	0.417	4170	0.5	0.01	49	10	2	34	1	9	0.2	3.0	56	0.01
KL18-10	480	483	0.95	9500	1.63	1.6	76	10	1	34	3	9	0.01	4.5	93	0.01
KL18-10	483	486	1.51	15100	2.28	2.3	104	9	2	43	2	12	0.5	6.5	79	0.01
KL18-10	486	489	1.07	10700	1.24	2.3	77	11	2	68	1	16	0.2	6.3	112	0.01
KL18-10	489	492	1.24	12400	1.19	2.1	110	17	3	54	1	16	0.3	5.3	60	0.01
KL18-10	492	495	1.5	15000	1.44	2.1	115	5	2	234	1	17	0.01	4.6	122	0.01
KL18-10	495	498	0.565	5650	0.54	0.7	36	9	4	69	1	8	0.01	4.8	57	0.01
KL18-10	498	501	0.54	5400	0.56	0.8	65	11	3	197	1	10	0.01	4.0	83	0.01
KL18-10	501	504	0.56	5600	0.64	1.2	74	11	6	118	1	12	0.3	4.4	50	0.01
KL18-10	504	507	0.69	6900	0.95	1.4	73	9	3	31	0.01	13	0.01	4.8	91	0.01
KL18-10	507	510	0.25	2500	0.43	1.4	38	12	2	39	0.01	8	0.01	4.5	60	0.01
KL18-10	510	513	0.213	2130	0.21	0.6	37	13	3	20	0.01	9	0.01	4.8	88	0.01
KL18-10	513	516	0.297	2970	0.3	1	41	9	2	24	1	8	0.01	4.5	41	0.01
KL18-10	516	519	0.28	2800	0.2	0.01	50	5	2	55	1	12	0.01	5.7	89	0.01
KL18-10	519	522	0.476	4760	0.6	0.7	83	6	1	78	0.01	10	0.01	6.0	56	0.01
KL18-10	522	525	0.24	2400	0.34	0.6	57	15	3	25	0.01	8	0.01	4.3	90	0.01
KL18-10	525	528	0.265	2650	0.47	1	105	9	2	35	0.01	5	0.01	3.2	34	0.01
KL18-10	528	531	0.54	5400	0.53	1	255	10	6	76	2	7	0.2	6.5	95	0.01
KL18-10	531	534	0.45	4500	0.25	0.9	121	7	16	51	0.01	7	0.01	7.0	50	0.01
KL18-10	534	537	0.47	4700	0.28	1.4	84	12	27	87	0.01	10	0.2	4.5	73	0.01
KL18-10	537	540	0.489	4890	0.57	0.8	83	8	5	56	0.01	11	0.2	5.5	52	0.01
KL18-10	540	543	0.334	3340	0.41	0.6	61	9	3	34	1	7	0.01	5.5	48	0.01
KL18-10	543	546	0.325	3250	0.49	0.6	56	8	1	21	1	6	0.01	5.5	47	0.01
KL18-10	546	549	0.178	1780	0.26	0.6	61	9	3	32	1	6	0.01	4.3	40	0.01
KL18-10	549	552	0.126	1260	0.18	0.01	40	7	3	69	0.01	6	0.01	3.2	44	0.01
KL18-10	552	555	0.124	1240	0.14	0.01	31	8	7	50	0.01	4	0.01	2.0	37	0.01
KL18-10	555	558	0.245	2450	0.25	0.7	41	6	1	81	0.01	3	0.01	3.1	41	0.01
KL18-10	558	561	0.28	2800	0.27	1	53	9	1	159	1	5	0.01	3.5	40	0.01
KL18-10	561	563	0.176	1760	0.21	0.7	39	8	1	56	0.01	5	0.01	3.5	57	0.01
KL18-10	563	566	0.105	1050	0.13	0.01	31	7	0.01	37	0.01	7	0.01	2.3	44	0.01
KL18-10	566	569	0.21	2100	0.15	0.01	183	21	4	34	1	10	0.01	3.3	69	0.01
KL18-10	569	572	0.23	2300	0.24	0.01	207	20	3	22	1	10	0.01	2.8	54	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL18-10	572	575	0.299	2990	0.33	0.6	386	19	5	67	2	10	0.01	4.3	84	0.01
KL18-10	575	578	0.2	2000	0.21	0.01	201	12	2	96	1	10	0.01	3.5	62	0.01
KL18-10	578	580.1	0.136	1360	0.08	0.01	73	16	5	43	1	4	0.3	2.3	93	0.01
KL18-10	580.1	582	0.334	3340	0.31	0.8	276	21	4	157	1	7	0.01	3.5	67	0.01
KL18-10	582	585	0.555	5550	0.44	1.3	97	11	6	120	2	10	0.01	4.9	64	0.01
KL18-10	585	588	0.26	2600	0.23	0.01	60	6	2	17	1	8	0.2	3.8	68	0.01
KL18-10	588	591	0.159	1590	0.13	0.01	46	7	2	23	1	7	0.01	2.8	64	0.01
KL18-10	591	594	0.09	900	0.07	0.01	60	14	1	24	1	4	0.01	1.5	63	0.01
KL18-10	594	597	0.078	780	0.05	0.01	105	18	1	19	1	5	0.01	1.5	57	0.01
KL18-10	597	600	0.094	940	0.06	0.01	60	13	3	30	1	6	0.01	1.8	59	0.01
KL18-10	600	603	0.082	820	0.07	0.01	70	34	2	51	1	5	0.01	1.3	53	0.01
KL18-10	603	606	0.083	830	0.05	0.01	47	14	4	24	1	5	0.01	2.0	63	0.01
KL18-10	606	609	0.119	1190	0.08	0.01	41	6	3	20	1	8	0.01	2.0	76	0.01
KL18-10	609	612	0.081	810	0.06	0.01	41	15	2	28	0.01	6	0.01	2.0	65	0.01
KL18-10	612	615	0.099	990	0.09	0.01	133	8	1	52	1	7	0.3	2.3	84	0.01
KL18-10	615	618	0.257	2570	0.15	0.8	620	51	3	83	1	9	0.5	4.9	92	0.01
KL18-10	618	621	0.096	960	0.09	0.01	59	14	1	37	1	8	1.5	2.8	91	0.01
KL18-10	621	624	0.149	1490	0.12	0.01	37	7	2	30	1	11	0.01	4.5	84	0.01
KL18-10	624	627	0.115	1150	0.09	0.01	85	31	2	61	1	10	0.01	2.9	98	0.01
KL18-10	627	630	0.162	1620	0.14	0.01	48	8	2	84	1	13	0.01	7.0	97	0.01
KL18-10	630	633	0.193	1930	0.15	1.4	40	43	3	111	1	12	0.01	5.3	95	0.01
KL18-10	633	636	0.311	3110	0.24	1.3	58	25	2	119	1	15	0.5	6.8	104	0.01
KL18-10	636	638	0.181	1810	0.18	0.01	49	8	0.01	88	2	13	0.01	4.3	116	0.01
KL18-10	638	641	0.221	2210	0.17	0.01	56	9	2	42	1	9	0.01	3.8	119	0.01
KL18-10	641	644	0.152	1520	0.14	0.01	51	9	0.01	31	1	8	0.01	3.1	120	0.01
KL18-10	644	646	0.071	710	0.07	0.01	43	9	1	18	1	6	0.01	1.8	181	0.01
KL18-10	646	648	0.066	660	0.04	0.01	28	9	0.01	13	1	6	0.2	2.0	179	0.01
KL18-10	648	651	0.077	770	0.07	0.01	25	9	1	29	1	7	0.2	2.8	208	0.01
KL18-10	651	654	0.19	1900	0.18	0.9	40	6	0.01	37	1	10	0.01	3.7	195	0.01
KL18-10	654	657	0.158	1580	0.16	0.01	40	8	0.01	14	1	10	0.01	1.0	123	0.01
KL18-10	657	660	0.151	1510	0.13	0.01	40	7	1	26	1	15	0.01	3.5	81	0.01
KL18-10	660	663	0.137	1370	0.12	0.01	35	10	2	37	1	14	0.2	3.0	81	0.01
KL18-10	663	666	0.096	960	0.09	0.01	30	8	1	40	0.01	12	0.01	3.3	89	0.01
KL18-10	666	669	0.125	1250	0.12	0.01	39	6	1	31	0.01	8	0.01	2.3	90	0.01
KL18-10	669	672	0.29	2900	0.2	0.8	52	14	2	36	1	7	0.01	4.0	88	0.01
KL18-10	672	675	0.138	1380	0.09	0.01	38	8	2	26	0.01	8	0.01	3.8	90	0.01
KL18-10	675	678	0.153	1530	0.14	0.01	38	7	1	37	0.01	8	0.01	4.3	69	0.01
KL18-10	678	681	0.132	1320	0.09	0.01	37	5	4	50	1	9	0.01	3.8	86	0.01
KL18-10	681	683.6	0.24	2400	0.17	0.01	54	5	7	71	1	9	0.01	4.5	90	0.01
KL18-10	683.6	686.6	0.175	1750	0.15	0.01	45	8	7	48	1	5	0.01	3.3	218	0.01
KL18-10	686.6	688.2	0.153	1530	0.13	0.01	43	10	4	66	0.01	4	0.01	3.4	219	0.01
KL18-10	688.2	690	0.438	4380	0.28	1.2	95	7	58	59	1	9	4.2	6.7	169	0.01
KL18-10	690	693	0.352	3520	0.22	0.9	89	15	62	46	1	6	5.7	3.3	204	0.2
KL18-10	693	696	0.085	850	0.09	0.01	43	11	3	18	1	3	0.2	1.6	59	0.01
KL18-10	696	699	0.0302	302	0.01	0.01	27	17	2	11	0.01	3	0.3	0.5	49	0.01
KL18-10	699	702	0.0354	354	0.03	0.01	35	10	0.01	7	0.01	2	0.3	0.5	48	0.01
KL18-10	702	705	0.083	830	0.06	0.01	65	15	9	5	3	4	1	0.0	56	0.01
KL18-10	705	708	0.109	1090	0.24	0.01	39	20	4	6	2	2	0.3	1.5	60	0.01
KL18-10	708	711	0.06	600	0.04	0.01	42	17	7	16	2	3	1.3	0.0	121	0.01
KL18-10	711	714	0.0309	309	0.02	0.01	34	25	4	0.01	1	2	0.2	0.5	98	0.01
KL18-10	714	717	0.057	570	0.08	0.01	26	8	5	5	1	3	0.01	0.7	68	0.01
KL18-10	717	720	0.145	1450	0.32	0.01	42	10	3	3	1	3	0.01	1.3	67	0.01
KL18-10	720	723	0.046	460	0.05	0.01	23	5	5	7	0.01	3	0.01	0.5	117	0.01
KL18-10	723	725.2	0.084	840	0.08	0.01	31	8	24	147	0.01	2	0.5	1.3	106	0.01
KL18-10	725.2	727	0.185	1850	0.12	3.6	61	56	55	66	0.01	5	26	2.8	381	0.55
KL18-10	727	729	0.24	2400	0.21	0.8	51	50	34	57	0.01	6	11.4	2.1	221	0.15
KL18-10	729	732	0.56	5600	0.58	3	179	208	92	27	1	8	16	2.8	123	0.17
KL18-10	732	735	0.44	4400	0.36	1	72	26	30	45	0.01	9	3.1	2.8	48	0.01
KL18-10	735	738	0.374	3740	0.43	0.8	78	48	36	33	0.01	7	3.8	4.9	208	0.01
KL18-10	738	741	0.24	2400	0.29	0.01	48	20	17	53	0.01	6	1.1	1.8	197	0.01
KL18-10	741	744	0.434	4340	0.39	1.5	57	28	27	37	0.01	8	5.2	3.0	240	0.01
KL18-10	744	747	0.34	3400	0.29	0.8	81	39	38	43	0.01	8	1.7	2.3	165	0.01
KL18-10	747	750	0.24	2400	0.16	0.01	63	39	37	27	0.01	12	5.3	3.6	173	0.1

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL18-10	750	753	0.26	2600	0.17	0.01	35	9	5	92	0.01	14	0.01	3.2	362	0.01
KL18-10	753	756	0.231	2310	0.21	0.8	46	8	13	42	0.01	8	4.4	3.6	374	0.12
KL18-10	756	759	0.369	3690	0.34	3.4	71	20	37	34	0.01	9	13.2	4.0	267	0.56
KL18-10	759	762	0.344	3440	0.25	0.7	43	7	15	29	0.01	16	0.9	4.3	391	0.01
KL18-10	762	765	0.275	2750	0.21	0.6	49	6	18	23	0.01	12	2.2	3.4	400	0.01
KL18-10	765	768	0.201	2010	0.14	0.01	44	7	21	35	0.01	11	0.7	3.0	364	0.01
KL18-10	768	771	0.169	1690	0.12	0.01	40	8	25	52	0.01	10	2.5	2.2	287	0.1
KL18-10	771	774	0.174	1740	0.12	0.8	64	12	37	28	0.01	8	3.8	4.1	260	0.01
KL18-10	774	777	0.117	1170	0.07	0.01	35	6	16	11	0.01	6	2.4	3.8	285	0.01
KL18-10	777	779.1	0.182	1820	0.15	0.01	36	6	23	14	0.01	7	0.8	3.0	388	0.01
KL18-10	779.1	781.9	0.18	1800	0.12	0.5	50	7	5	26	0.01	5	0.01	2.2	251	0.01
KL18-10	781.9	783.7	0.42	4200	0.33	7.9	82	8	110	125	1	7	54	3.4	240	1.73
KL18-10	783.7	786	0.126	1260	0.12	0.01	29	5	22	14	0.01	4	1.5	1.6	67	0.1
KL18-10	786	789	0.174	1740	0.1	0.7	35	7	31	21	0.01	3	5.8	2.1	61	0.17
KL18-10	789	792	0.229	2290	0.16	1.9	51	9	92	14	0.01	8	30	3.4	247	0.61
KL18-10	792	795	0.18	1800	0.09	1.7	50	12	66	18	0.01	4	14	2.4	71	0.48
KL18-10	795	798	0.152	1520	0.14	0.01	54	15	15	27	0.01	5	0.5	2.5	146	0.01
KL18-10	798	801	0.18	1800	0.17	0.01	57	19	16	39	0.01	7	0.9	2.4	72	0.1
KL18-10	801	804	0.16	1600	0.15	0.01	34	6	8	12	0.01	5	0.01	1.9	46	0.01
KL18-10	804	807	0.33	3300	0.28	1	62	5	2	17	0.01	4	0.01	2.7	201	0.01
KL18-10	807	810	0.26	2600	0.19	1.4	50	16	16	12	0.01	5	2.1	2.3	41	0.19
KL18-10	810	813	0.185	1850	0.17	0.9	36	0.01	16	18	0.01	6	3.8	3.3	45	0.1
KL18-10	813	816	0.198	1980	0.17	0.9	39	0.01	17	18	0.01	7	2.9	2.3	42	0.11
KL18-10	816	819	0.238	2380	0.19	1	51	10	9	38	0.01	7	0.7	3.1	55	0.01
KL18-10	819	822	0.205	2050	0.15	1.5	46	11	14	18	0.01	8	5.2	2.8	236	0.01
KL18-10	822	825	0.23	2300	0.17	0.9	49	11	22	15	0.01	6	2.4	2.2	256	0.19
KL18-10	825	828	0.152	1520	0.12	0.01	29	9	2	15	0.01	5	0.01	1.4	50	0.01
KL18-10	828	831	0.22	2200	0.18	1.8	77	26	45	27	0.01	4	7.5	1.8	61	0.14
KL18-10	831	834	0.145	1450	0.1	2.1	107	131	46	18	0.01	3	10.6	1.9	36	0.2
KL18-10	834	837	0.175	1750	0.13	0.8	46	15	9	16	0.01	6	0.7	2.0	60	0.01
KL18-10	837	840	0.137	1370	0.13	0.6	33	7	2	12	0.01	8	0.01	2.2	75	0.01
KL18-10	840	843	0.182	1820	0.18	0.7	35	9	2	17	0.01	7	0.01	2.9	60	0.01
KL18-10	843	846	0.143	1430	0.13	3	55	47	28	29	0.01	5	8.8	1.7	65	0.49
KL18-10	846	849	0.136	1360	0.1	0.6	38	12	7	31	0.01	8	0.8	2.3	167	0.01
KL18-10	849	852	0.138	1380	0.08	0.01	33	10	12	13	0.01	6	1	1.9	67	0.01
KL18-10	852	855	0.149	1490	0.09	3.6	45	18	25	10	1	9	11.5	2.3	63	0.01
KL18-10	855	858	0.153	1530	0.12	18.8	70	110	75	14	5	5	42	1.5	46	1.57
KL18-10	858	859.9	0.254	2540	0.27	1.8	32	9	3	12	0.01	14	0.5	2.1	50	0.01
KL18-10	859.9	861.8	0.101	1010	0.01	0.01	41	7	2	7	0.01	20	0.01	1.4	16	0.01
KL18-10	861.8	864.5	0.046	460	0.01	0.01	31	7	2	7	0.01	19	0.01	0.9	18	0.01
KL18-10	864.5	867	0.068	680	0.02	0.01	19	8	1	7	0.01	16	0.01	1.5	20	0.01
KL18-10	867	870	0.079	790	0.01	0.01	24	14	2	14	0.01	15	0.01	1.5	75	0.01
KL18-10	870	872	0.064	640	0.01	0.01	29	20	2	6	0.01	13	0.7	0.9	73	0.01
KL18-10	872	874	0.037	370	0.01	0.01	35	8	0.01	3	0.01	13	0.01	0.5	78	0.01
KL18-10	874	876	0.056	560	0.01	0.01	45	11	1	8	0.01	13	0.2	1.0	47	0.01
KL18-10	876	879	0.0214	214	0.01	0.01	30	8	0.01	12	0.01	9	0.01	0.0	73	0.01
KL18-10	879	882	0.0388	388	0.02	0.01	31	11	0.01	2	0.01	10	0.01	0.0	74	0.01
KL18-10	882	885	0.075	750	0.02	0.01	33	11	0.01	2	0.01	18	0.01	0.8	97	0.01
KL20-01	0	4.4	0.0375	375	0.09	0.9	73	39	10	9	0.01	0.01	0.6	2.4	21	0.01
KL20-01	4.4	7.4	0.0053	53	0.01	0.01	172	188	3	8	0.01	0.01	0.01	1.7	20	0.01
KL20-01	7.4	10.4	0.0211	211	0.01	0.01	72	120	1	8	0.01	0.01	0.2	2.9	21	0.01
KL20-01	10.4	13.4	0.0084	84	0.01	0.6	139	195	3	8	0.01	0.01	0.6	1.9	29	0.01
KL20-01	13.4	16.4	0.0065	65	0.01	0.01	81	129	1	6	0.01	0.01	0.2	0.9	22	0.01
KL20-01	16.4	19.4	0.0049	49	0.01	0.01	93	313	2	7	0.01	0.01	0.6	1.7	23	0.01
KL20-01	19.4	22.4	0.0022	22	0.03	1	338	470	9	6	0.01	0.01	0.5	2.1	25	0.01
KL20-01	22.4	25.4	0.0028	28	0.01	1.1	190	920	3	7	0.01	0.01	0.8	1.9	31	0.01
KL20-01	25.4	28.4	0.0023	23	0.01	1.2	800	980	2	7	0.01	0.01	1.2	3.5	26	0.01
KL20-01	28.4	31.4	0.002	20	0.01	0.01	234	338	2	0.01	0.01	0.01	0.5	0.6	27	0.01
KL20-01	31.4	34.4	0.0023	23	0.04	2.4	407	960	4	5	0.01	0.01	0.8	3.3	41	0.01
KL20-01	34.4	37.4	0.0019	19	0.01	1.6	354	670	2	0.01	0.01	0.01	0.3	1.8	29	0.01
KL20-01	37.4	40.4	0.0026	26	0.01	1.5	401	540	4	7	0.01	0.01	0.6	5.9	24	0.01
KL20-01	40.4	43.4	0.002	20	0.01	1.9	154	171	6	16	0.01	0.01	0.4	2.0	18	0.01
KL20-01	43.4	46.4	0.0026	26	0.01	1.5	178	147	5	29	0.01	0.01	0.3	1.9	20	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL20-01	46.4	49.4	0.0021		21	0.01	0.01	342	132	3	13	0.01	0.01	0.01	1.2	12	0.01
KL20-01	49.4	52.4	0.0033		33	0.01	2.3	530	460	7	13	0.01	0.01	0.7	4.3	17	0.01
KL20-01	52.4	55.4	0.0019		19	0.01	1	96	194	2	4	0.01	0.01	0.01	1.0	14	0.01
KL20-01	55.4	58.4	0.0034		34	0.01	0.9	109	130	2	4	0.01	0.01	0.01	1.0	13	0.01
KL20-01	58.4	61.4	0.0022		22	0.01	2.9	580	295	5	7	0.01	0.01	0.3	2.3	17	0.01
KL20-01	61.4	64.4	0.0046		46	0.01	5.6	670	890	26	9	0.01	0.01	1.3	5.9	23	0.01
KL20-01	64.4	67.4	0.0083		83	0.02	8.3	1160	2400	29	24	0.01	0.01	3.3	13.8	24	0.01
KL20-01	67.4	70.4	0.0356		356	0.13	155	22100	26200	32	15	0.01	0.01	44	44.0	21	0.01
KL20-01	70.4	73.4	0.0038		38	0.01	6.7	1070	2100	7	10	7	0.01	1.6	10.0	17	0.01
KL20-01	73.4	76.4	0.0032		32	0.01	4.2	720	1760	12	7	2	0.01	1.1	11.5	17	0.01
KL20-01	76.4	79.4	0.0026		26	0.01	2.4	450	820	16	7	0.01	0.01	1	3.2	19	0.01
KL20-01	79.4	82.4	0.0063		63	0.01	5	2200	2325	12	11	2	0.01	4.5	9.4	19	0.01
KL20-01	82.4	85.4	0.0124		124	0.01	7.1	3920	3375	23	13	2	0.01	10	9.8	15	0.01
KL20-01	85.4	88.4	0.0073		73	0.04	4.5	540	510	83	13	2	2	1.3	7.8	26	0.51
KL20-01	88.4	91.4	0.0225		225	0.02	3.1	720	860	12	10	2	2	0.8	6.6	18	0.01
KL20-01	91.4	94.4	0.0132		132	0.02	30.7	3600	7200	21	21	62	0.01	5.1	49.0	18	0.01
KL20-01	94.4	96.6	0.0233		233	0.07	26	3600	2575	360	196	42	5	5.8	29.3	45	0.01
KL20-01	96.6	100.4	0.0101		101	0.04	4.2	1010	1680	19	11	6	0.01	0.7	10.0	15	0.01
KL20-01	100.4	103.4	0.0272		272	0.02	3.8	2600	1470	37	18	4	0.01	2.7	7.6	16	0.01
KL20-01	103.4	106.4	0.0133		133	0.03	4.8	3200	3825	41	13	3	0.01	8.5	7.5	14	0.15
KL20-01	106.4	109.4	0.0139		139	0.01	8.3	3700	2200	22	13	15	0.01	2.2	7.5	14	0.1
KL20-01	109.4	112.4	0.0147		147	0.04	8.2	5400	6500	27	10	6	0.01	5.5	33.0	18	0.1
KL20-01	112.4	115.4	0.67		6700	0.48	360	26000	103000	210	13	1180	6	14.4	627.0	42	0.01
KL20-01	115.4	116.9	0.0371		371	0.21	37	6900	15300	140	20	77	3	13.3	72.5	23	0.01
KL20-01	116.9	119.9	0.093		930	0.2	61	8300	28700	46	29	150	0.01	5.8	63.8	15	0.01
KL20-01	119.9	122.9	0.0231		231	0.12	7	6700	4530	43	13	7	0.01	6.3	8.8	17	0.01
KL20-01	122.9	124.8	0.425		4250	0.68	153	278000	150400	99	27	204	7	100	420.0	64	0.01
KL20-01	124.8	127.4	0.0306		306	0.09	43	7600	7000	11	243	170	4	1.5	58.0	42	0.01
KL20-01	127.4	130.4	0.0234		234	0.02	2.3	3300	880	27	119	10	5	0.3	10.7	33	0.01
KL20-01	130.4	133.4	0.0133		133	0.02	0.8	610	330	11	392	3	2	0.4	5.6	21	0.01
KL20-01	133.4	136.4	0.051		510	0.27	1	2100	111	9	4	2	3	0.01	3.2	18	0.01
KL20-01	136.4	139.4	0.0184		184	0.02	1.1	630	379	14	12	4	3	0.2	2.2	18	0.01
KL20-01	139.4	142.4	0.073		730	0.24	2.3	4900	322	11	12	6	5	0.4	6.1	22	0.01
KL20-01	142.4	145.4	0.049		490	0.08	0.9	2600	194	11	20	5	4	0.01	3.8	41	0.01
KL20-01	145.4	148.4	0.05		500	0.1	0.6	4000	147	19	27	4	4	1	4.8	29	0.01
KL20-01	148.4	151.4	1.04		10400	0.23	13.6	50200	29300	7	26	85	11	6.5	14.0	35	0.01
KL20-01	151.4	154.4	0.096		960	0.08	0.9	4300	321	6	438	2	13	0.01	5.1	30	0.01
KL20-01	154.4	157.4	0.184		1840	0.38	1.1	61700	97	22	49	0.01	108	0.01	34.8	30	0.01
KL20-01	157.4	160.4	0.22		2200	0.53	0.9	105000	85	20	10	1	262	0.5	38.0	26	0.01
KL20-01	160.4	163.4	0.38		3800	0.09	0.8	9300	67	5	21	0.01	44	0.01	8.5	17	0.01
KL20-01	163.4	166.4	0.71		7100	1.01	1.5	6700	52	36	64	1	58	0.01	10.6	34	0.01
KL20-01	166.4	169.4	0.66		6600	0.91	1.2	29300	32	31	51	2	54	5.3	24.0	18	0.01
KL20-01	169.4	172.4	1.46		14600	1.43	1.9	2400	16	22	260	1	39	0.01	14.0	18	0.01
KL20-01	172.4	175.4	0.68		6800	0.85	2.6	174	54	5	525	19	8	0.3	10.2	17	0.01
KL20-01	175.4	178.4	0.088		880	0.27	0.01	72	19	4	398	2	6	0.2	3.9	18	0.01
KL20-01	178.4	181.4	0.086		860	0.47	0.01	53	14	6	2030	0.01	4	0.01	4.6	24	0.01
KL20-01	181.4	184.4	0.0372		372	0.06	0.01	123	16	3	36	0.01	5	0.01	1.1	9	0.01
KL20-01	184.4	187.4	0.19		1900	0.11	0.5	193	17	9	52	0.01	7	0.2	3.9	0	0.01
KL20-01	187.4	190.4	1.16		11600	1.46	6.7	560	6	17	8	18	27	0.01	5.5	38	0.01
KL20-01	190.4	193.9	0.76		7600	0.4	4.8	1280	28	11	6	10	47	1.1	3.6	18	0.01
KL20-01	193.9	197.2	0.118		1180	0.08	1.3	540	0.01	3	3	3	11	0.01	0.0	14	0.01
KL20-01	197.2	200.3	1.83		18300	0.98	18.1	1650	40	12	3	38	106	1.2	9.0	20	0.01
KL20-01	200.3	203.9	0.08		800	0.04	0.6	264	23	6	25	2	10	0.01	0.0	14	0.01
KL20-01	203.9	206.9	0.142		1420	0.04	0.7	318	0.01	8	4	1	4	0.01	0.0	12	0.01
KL20-01	206.9	209.9	0.041		410	0.01	0.8	420	6	4	4	0.01	3	0.01	0.0	13	0.01
KL20-01	209.9	211.2	0.076		760	0.08	0.01	216	0.01	13	5	0.01	10	0.01	0.0	12	0.01
KL20-01	211.2	214.4	2.06		20600	0.92	7.2	1940	22	45	5	7	135	0.8	25.5	14	0.01
KL20-01	214.4	217.4	3.04		30400	1.04	9.5	286	10	46	7	10	38	1.6	13.0	18	0.01
KL20-01	217.4	220.4	0.0252		252	0.01	0.01	253	0.01	30	2	0.01	2	0.01	0.0	12	0.01
KL20-01	220.4	223.4	0.177		1770	0.07	1.1	304	0.01	30	2	0.01	5	0.4	0.0	15	0.01
KL20-01	223.4	226.4	0.045		450	0.01	0.01	270	0.01	36	2	0.01	0.01	0.01	0.0	12	0.01
KL20-01	226.4	228.6	0.179		1790	0.05	1.3	262	0.01	45	3	1	3	0.01	0.0	9	0.01
KL20-01	228.6	231.9	0.059		590	0.05	0.5	460	0.01	11	2	1	5	0.01	0.0	10	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL20-01	231.9	234.9	1.63	16300	4.67	7.2	319	14	9	0.01	12	20	0.01	13.5	40	0.01
KL20-01	234.9	237.3	1.95	19500	4.23	6	187	10	27	7	10	24	0.9	17.0	20	0.01
KL20-01	237.3	241	2.06	20600	5.41	5.7	105	12	8	6	11	21	0.2	17.5	34	0.01
KL20-01	241	244.4	1.01	10100	1.1	1.3	163	6	1	21	1	48	0.7	6.5	30	0.01
KL20-01	244.4	247.4	1.67	16700	1.79	2.1	193	0.01	8	124	1	55	0.2	6.0	40	0.01
KL20-01	247.4	250.4	3.5	35000	5.67	6.4	136	10	2	6	7	31	13	25.2	37	0.01
KL20-01	250.4	253.4	0.473	4730	0.43	1.2	73	11	3	4	1	13	0.4	4.5	24	0.01
KL20-01	253.4	256.4	0.54	5400	0.49	0.9	113	8	11	26	0.01	18	0.9	6.0	27	0.01
KL20-01	256.4	259.4	1.26	12600	0.73	1.8	86	8	13	17	1	30	0.4	18.2	41	0.01
KL20-01	259.4	262.4	1.9	19000	1.63	2	157	6	2	5	2	56	0.01	9.0	49	0.01
KL20-01	262.4	266.4	1.34	13400	1.53	1.7	98	8	6	34	2	33	0.01	5.5	88	0.01
KL20-01	266.4	268.4	0.71	7100	0.72	1.2	46	9	4	270	3	14	0.01	3.6	73	0.01
KL20-01	268.4	271.4	0.91	9100	1.4	1.3	62	9	4	51	2	16	0.2	4.2	86	0.01
KL20-01	271.4	274.4	1.02	10200	0.8	1.6	95	12	3	42	1	25	0.5	6.0	78	0.01
KL20-01	274.4	277.4	1.17	11700	1.55	1.6	58	7	19	33	1	19	0.2	8.5	85	0.01
KL20-01	277.4	280.4	0.94	9400	1.02	1.2	47	8	4	110	0.01	20	0.01	6.5	107	0.01
KL20-01	280.4	283.4	0.96	9600	0.46	1.6	67	27	13	139	1	14	0.01	4.0	50	0.01
KL20-01	283.4	286.4	0.85	8500	0.65	1.6	63	12	7	115	1	24	0.01	5.0	71	0.01
KL20-01	286.4	289.4	0.79	7900	0.62	1.4	58	10	4	151	1	19	1.2	4.2	101	0.01
KL20-01	289.4	292.4	0.79	7900	0.76	1.4	50	8	1	82	1	17	0.01	4.1	102	0.01
KL20-01	292.4	295.4	1.11	11100	1.57	2.9	61	25	4	30	3	13	0.9	9.5	68	0.01
KL20-01	295.4	298.4	1.1	11000	0.67	4.2	430	154	43	128	2	26	2.5	12.0	55	0.01
KL20-01	298.4	301.4	1.05	10500	1	2.2	78	21	4	84	2	18	0.01	7.5	81	0.01
KL20-01	301.4	304.4	0.88	8800	0.85	1.6	70	20	0.01	91	1	18	0.01	4.8	94	0.01
KL20-01	304.4	307.4	0.84	8400	0.81	1.2	65	11	0.01	20	1	16	0.2	4.2	75	0.01
KL20-01	307.4	310.4	0.85	8500	1.11	1.6	66	11	0.01	77	1	17	0.01	4.8	106	0.01
KL20-01	310.4	313.4	0.57	5700	0.54	0.9	57	6	0.01	53	0.01	17	0.2	4.8	97	0.01
KL20-01	313.4	316.4	0.62	6200	0.53	1.1	66	10	2	75	0.01	13	0.3	3.8	90	0.01
KL20-01	316.4	319.4	0.502	5020	0.45	0.8	60	6	0.01	54	0.01	12	0.01	4.4	85	0.01
KL20-01	319.4	322.4	0.62	6200	0.52	0.9	68	6	0.01	46	0.01	15	0.01	1.8	73	0.01
KL20-01	322.4	325.4	0.401	4010	0.45	0.5	50	8	0.01	19	0.01	9	0.4	3.5	92	0.01
KL20-01	325.4	328.4	0.324	3240	0.38	0.01	47	12	1	52	0.01	9	0.7	2.4	104	0.01
KL20-01	328.4	331.4	0.6	6000	0.42	0.7	61	8	0.01	25	0.01	13	0.4	3.4	98	0.01
KL20-01	331.4	334.4	0.97	9700	0.92	1.7	74	12	33	60	1	17	2.1	5.0	67	0.01
KL20-01	334.4	337.4	0.98	9800	0.69	0.9	82	29	160	124	1	18	2.5	3.0	68	0.01
KL20-01	337.4	340.4	0.885	8850	0.7	1.8	78	12	3	82	1	20	0.7	5.6	92	0.01
KL20-01	340.4	343.4	1.27	12700	0.5	3.2	111	27	6	138	1	18	2.1	4.3	62	0.01
KL20-01	343.4	346.4	1.56	15600	1.22	3.5	139	20	2	253	1	24	0.5	6.0	90	0.01
KL20-01	346.4	349.1	0.557	5570	0.48	1.1	90	17	5	52	1	20	0.2	5.6	65	0.01
KL20-01	349.1	352.3	1.06	10600	0.8	2	108	24	2	23	1	31	0.3	9.5	61	0.01
KL20-01	352.3	355.4	0.475	4750	0.41	0.8	80	20	4	64	0.01	11	0.01	4.8	46	0.01
KL20-01	355.4	358.4	0.83	8300	1.08	1.4	102	17	4	289	0.01	23	0.01	7.0	66	0.01
KL20-01	358.4	359.9	1.28	12800	2.43	2.5	118	15	1	301	0.01	22	0.01	5.5	58	0.01
KL20-01	359.9	362.9	0.63	6300	0.51	1.5	52	22	12	37	0.01	8	0.3	4.2	64	0.01
KL20-01	362.9	365.9	0.78	7800	1.25	1.4	34	17	3	16	2	6	0.01	4.0	70	0.01
KL20-01	365.9	368.9	0.72	7200	0.52	1.9	93	38	28	32	1	5	1.1	4.2	49	0.01
KL20-01	368.9	371.9	0.6	6000	0.55	1.3	72	28	56	20	2	6	1.1	4.4	57	0.01
KL20-01	371.9	374.9	0.518	5180	0.39	7	2140	2300	490	6	3	4	64	5.0	180	0.35
KL20-01	374.9	377.9	0.98	9800	1.4	2.3	45	19	7	9	3	6	1.6	5.5	186	0.01
KL20-01	377.9	380.9	0.68	6800	0.68	1.4	54	8	3	16	1	10	0.3	3.2	87	0.01
KL20-01	380.9	383.9	0.58	5800	1.1	1.4	41	11	8	22	2	8	0.5	3.8	164	0.01
KL20-01	383.9	386.9	0.77	7700	1.66	3.1	177	580	16	13	3	5	5.2	5.0	73	0.01
KL20-01	386.9	389.9	0.68	6800	0.9	1.2	23	13	2	24	1	5	0.4	3.6	197	0.01
KL20-01	389.9	392.9	0.675	6750	1.22	1.4	30	14	0.01	14	1	4	1.5	4.4	81	0.01
KL20-01	392.9	395.9	0.85	8500	0.84	4.8	930	297	140	14	3	4	48	7.0	100	0.01
KL20-01	395.9	398.9	0.448	4480	1.16	0.8	54	29	4	8	2	3	2.4	4.4	157	0.01
KL20-01	398.9	401.9	0.72	7200	1.36	1.4	57	25	9	16	1	5	1.8	4.4	161	0.01
KL20-01	401.9	404.9	0.56	5600	0.45	5	640	269	25	36	2	6	9.2	3.5	123	0.01
KL20-01	404.9	407.9	1.46	14600	0.21	23.9	880	750	750	12	12	5	355	4.3	100	0.01
KL20-01	407.9	410.9	0.59	5900	0.31	2.7	245	285	320	13	2	6	9.9	5.0	127	0.01
KL20-01	410.9	413.9	0.89	8900	0.87	3.5	79	64	24	19	2	5	3.4	6.0	143	0.01
KL20-01	413.9	416.6	0.56	5600	0.57	2.7	108	66	18	22	1	6	3.9	2.8	157	0.01
KL20-02	0	2	0.0066	66	0.05	2.4	257	151	13	13	0.01	0.01	1.1	3.2	28	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL20-02	2	4	0.0045		45	0.1	0.9	82	69	23	4	0.01	0.01	0.9	1.3	32	0.01
KL20-02	4	7	0.0031		31	0.01	1	95	150	4	3	0.01	0.01	0.5	0.6	29	0.01
KL20-02	7	10	0.0038		38	0.01	0.01	33	55	1	3	0.01	0.01	0.3	4.1	29	0.01
KL20-02	10	13	0.003		30	0.02	0.01	103	130	3	4	0.01	0.01	0.5	2.5	35	0.01
KL20-02	13	16	0.0022		22	0.02	0.8	383	265	9	4	0.01	0.01	0.6	1.2	29	0.01
KL20-02	16	19	0.003		30	0.01	0.6	101	277	2	2	0.01	0.01	0.4	1.5	29	0.01
KL20-02	19	22	0.0025		25	0.01	0.8	99	410	4	2	0.01	0.01	0.7	2.8	33	0.01
KL20-02	22	25	0.0045		45	0.01	0.5	97	97	4	3	0.01	0.01	0.3	1.3	30	0.01
KL20-02	25	28	0.0024		24	0.01	1.8	530	660	5	3	0.01	0.01	0.9	1.6	29	0.01
KL20-02	28	31	0.002		20	0.01	2.1	187	221	6	4	0.01	0.01	0.5	2.0	34	0.01
KL20-02	31	34	0.0034		34	0.01	1.7	229	348	3	4	0.01	0.01	0.6	2.1	32	0.01
KL20-02	34	36.8	0.0063		63	0.1	5.1	1040	630	15	18	0.01	0.01	1	4.9	32	0.01
KL20-02	36.8	38.5	0.0042		42	0.01	3.6	1310	820	9	8	0.01	0.01	1.4	3.2	18	0.01
KL20-02	38.5	40	0.0036		36	0.01	0.5	159	101	6	6	0.01	0.01	0.01	0.9	19	0.01
KL20-02	40	42.6	0.0027		27	0.01	1.1	420	221	7	9	0.01	0.01	0.2	1.2	15	0.01
KL20-02	42.6	45.9	0.0014		14	0.01	0.8	248	139	5	5	0.01	0.01	0.01	1.0	17	0.01
KL20-02	45.9	48.7	0.0014		14	0.01	1.5	123	94	5	7	0.01	0.01	0.01	0.9	19	0.01
KL20-02	48.7	51	0.0023		23	0.01	1.5	173	148	6	2	0.01	0.01	0.01	1.0	15	0.01
KL20-02	51	54	0.0024		24	0.02	12.1	3800	2660	10	8	0.01	0.01	1.2	18.5	21	0.01
KL20-02	54	57	0.0022		22	0.01	1.7	580	520	10	4	0.01	0.01	0.8	1.9	19	0.01
KL20-02	57	59.5	0.0047		47	0.08	24.8	1590	2740	28	6	0.01	0.01	2.3	31.7	18	0.01
KL20-02	59.5	62.5	0.0025		25	0.01	8.5	730	1240	8	7	0.01	0.01	1.5	4.9	17	0.01
KL20-02	62.5	65.5	0.0106		106	0.01	36.8	28700	28900	29	7	0.01	0.01	47	27.8	22	0.01
KL20-02	65.5	67	0.0217		217	0.01	2.7	700	1340	5	5	0.01	0.01	1.7	8.8	17	0.01
KL20-02	67	70	0.0343		343	0.03	35.1	10600	26200	13	5	6	0.01	33	57.5	25	0.01
KL20-02	70	73	0.0238		238	0.01	1.2	550	840	3	4	0.01	0.01	1.4	2.3	22	0.01
KL20-02	73	76	0.0142		142	0.01	1.6	520	1190	6	6	0.01	0.01	1.6	4.8	19	0.01
KL20-02	76	79	0.0184		184	0.01	12.4	2300	2320	9	8	0.01	0.01	4	5.7	22	0.01
KL20-02	79	82	0.0057		570	0.22	164	7200	6100	26	6	0.01	0.01	24	19.5	21	0.01
KL20-02	82	84.8	0.0141		141	0.01	3.6	265	362	8	7	3	0.01	1.1	3.2	19	0.01
KL20-02	84.8	87.3	0.0072		72	0.04	3.9	440	540	8	9	0.01	0.01	1.3	3.6	25	0.01
KL20-02	87.3	88.5	0.0084		84	0.01	1.4	640	690	8	15	1	0.01	0.5	3.6	22	0.01
KL20-02	88.5	91.6	0.0304		304	0.05	2.2	640	335	20	9	2	0.01	1.3	2.1	31	0.01
KL20-02	91.6	94.8	0.0029		29	0.02	0.9	470	450	11	5	0.01	0.01	0.7	2.5	22	0.01
KL20-02	94.8	96.2	0.0123		123	0.01	3.1	4200	970	35	3	3	0.01	1.1	3.6	22	0.01
KL20-02	96.2	98.5	0.021		210	0.08	12.6	7100	17200	19	47	3	0.01	6	80.0	24	0.01
KL20-02	98.5	101.6	0.0263		263	0.03	8.2	5300	5800	38	61	1	0.01	4.8	15.3	26	0.01
KL20-02	101.6	105.7	0.0244		244	0.02	7.6	2500	4300	31	38	4	0.01	4.2	12.4	30	0.01
KL20-02	105.7	110.4	0.071		710	0.1	54.3	40600	59200	71	21	13	0.01	58	33.9	52	0.01
KL20-02	110.4	113	0.0256		256	0.17	11	14100	13700	290	23	4	0.01	13.7	12.7	25	0.01
KL20-02	113	114.5	0.18		1800	0.16	60.5	42500	38300	49	12	1	0.01	60	73.8	16	0.01
KL20-02	114.5	116.9	0.85		8500	0.45	92.9	71300	85200	120	127	64	2	63	256.0	141	0.01
KL20-02	116.9	119.5	0.0178		178	0.09	1.6	720	810	7	210	1	0.01	1.4	4.4	157	0.01
KL20-02	119.5	121	0.0072		72	0.02	1.3	920	1160	7	230	2	0.01	0.8	5.1	31	0.01
KL20-02	121	122.5	0.0048		48	0.04	0.5	230	270	7	490	1	0.01	0.3	2.9	64	0.01
KL20-02	122.5	124	0.0027		27	0.04	0.01	134	150	3	206	0.01	0.01	0.4	1.1	98	0.01
KL20-02	124	125.5	0.0277		277	0.2	0.9	930	78	6	3	0.01	0.01	0.7	1.2	9	0.01
KL20-02	125.5	127.8	0.122		1220	1.16	3.7	8000	87	10	5	112	5	1.2	6.7	18	0.01
KL20-02	127.8	130	0.131		1310	0.11	1.1	7000	170	11	123	230	5	0.6	6.8	24	0.01
KL20-02	130	133	0.21		2100	1.21	3.2	18400	130	20	7	90	9	1.7	11.5	27	0.01
KL20-02	133	134.5	0.21		2100	0.23	1.6	5400	214	8	56	16	12	1.2	5.6	21	0.01
KL20-02	134.5	137.5	1.44		14400	2.44	9.8	61800	540	7	40	13	61	2.6	19.9	31	0.01
KL20-02	137.5	140.5	0.21		2100	0.25	0.8	2300	194	9	220	2	10	0.5	4.9	23	0.01
KL20-02	140.5	143.5	1.04		10400	1.38	1.2	23300	58	12	94	9	75	1.5	19.2	48	0.01
KL20-02	143.5	146.5	0.21		2100	0.32	0.6	510	13	6	380	1	18	0.8	3.1	23	0.01
KL20-02	146.5	149.5	0.45		4500	0.72	0.8	420	28	4	280	3	8	0.7	5.5	29	0.01
KL20-02	149.5	152.5	0.46		4600	0.43	1	2900	38	7	50	1	14	0.3	5.4	25	0.01
KL20-02	152.5	155.5	0.7		7000	1.06	0.7	470	12	21	49	3	14	0.5	8.2	16	0.01
KL20-02	155.5	158.5	0.56		5600	0.79	0.8	295	17	14	37	6	15	0.3	7.8	20	0.01
KL20-02	158.5	160	0.39		3900	0.9	0.7	183	10	17	162	2	9	0.4	6.0	18	0.01
KL20-02	160	163	0.57		5700	0.82	1	315	10	10	160	2	12	0.5	5.8	32	0.01
KL20-02	163	166	0.55		5500	0.24	1.4	99	20	22	158	2	3	0.01	10.3	33	0.01
KL20-02	166	167.5	0.205		2050	0.09	0.7	230	41	16	27	1	2	0.4	4.0	19	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL20-02	167.5	171.5	3.38	33800	19.5	11.9	127000	30	16	11	113	87	0.01	71.9	31	0.01
KL20-02	171.5	173.5	0.57	5700	0.5	4.3	2200	13	8	10	10	26	0.3	10.7	19	0.01
KL20-02	173.5	177.2	0.51	5100	0.21	6.8	780	12	8	2	2	8	0.01	1.3	18	0.01
KL20-02	177.2	179.3	0.28	2800	0.22	2.4	630	17	8	5	1	0.01	0.3	3.0	16	0.01
KL20-02	179.3	182.5	0.45	4500	0.3	4.7	1170	12	7	3	5	12	0.01	3.8	18	0.01
KL20-02	182.5	185.4	1.54	15400	1.41	13.4	7700	15	10	0.01	8	47	0.2	10.8	21	0.01
KL20-02	185.4	187	0.165	1650	0.13	1.7	351	12	3	0.01	5	3	0.01	0.8	14	0.01
KL20-02	187	190	1.36	13600	0.56	8	610	14	6	3	24	70	1.5	5.8	35	0.01
KL20-02	190	193.4	1.16	11600	0.39	11	1000	15	5	0.01	22	68	1.7	3.0	31	0.01
KL20-02	193.4	195.5	0.058	580	0.07	0.01	301	10	4	9	1	4	1.6	1.0	12	0.01
KL20-02	195.5	197	0.0092	92	0.01	0.01	320	10	6	2	0.01	3	0.3	0.6	14	0.01
KL20-02	197	200.2	0.126	1260	0.12	1.2	1690	13	8	0.01	0.01	7	0.5	4.0	17	0.01
KL20-02	200.2	203.2	0.22	2200	0.15	2.8	3500	160	21	2	5	11	0.7	7.3	25	0.01
KL20-02	203.2	205.5	0.28	2800	0.07	3.6	250	18	19	2	3	3	0.3	1.8	20	0.01
KL20-02	205.5	209.5	2.98	29800	1.48	23.5	365	15	10	2	62	50	1.5	12.0	17	0.01
KL20-02	209.5	212.5	1.32	13200	1.35	2.6	119	36	83	27	4	38	0.4	18.8	22	0.01
KL20-02	212.5	214.4	1.39	13900	2.34	4.2	63	10	10	2	7	17	0.01	13.0	20	0.01
KL20-02	214.4	217	1.19	11900	1.22	2	61	10	0.01	0.01	2	17	0.01	18.9	12	0.01
KL20-02	217	220	0.81	8100	1.31	2.3	73	10	15	0.01	5	21	0.2	15.5	14	0.01
KL20-02	220	223	1.36	13600	0.78	2.5	850	288	6	6	0.01	40	0.2	19.0	19	0.01
KL20-02	223	226	0.36	3600	0.09	0.5	1300	73	7	9	0.01	12	0.01	37.1	31	0.01
KL20-02	226	229	0.55	5500	0.62	1.9	109	13	1	62	0.01	32	0.01	13.3	33	0.01
KL20-02	229	232	1.07	10700	0.94	1.6	90	45	5	15	20	32	0.5	11.5	32	0.01
KL20-02	232	235	2.38	23800	0.86	4	108	12	3	27	1	21	0.3	12.5	52	0.01
KL20-02	235	238	3.98	39800	7.32	8.4	78	12	1	31	6	34	0.3	23.8	73	0.01
KL20-02	238	240.6	1.99	19900	1.91	3.9	32	10	6	377	8	12	0.3	12.8	109	0.01
KL20-02	240.6	242.5	2.25	22500	2.31	8.7	32	12	1	82	9	19	0.3	20.0	65	0.01
KL20-02	242.5	245.5	2.17	21700	2.66	5.7	37	17	12	55	9	10	0.3	14.5	73	0.01
KL20-02	245.5	248.5	1.74	17400	1.29	5.2	55	67	60	197	5	6	2.6	9.3	126	0.01
KL20-02	248.5	251.5	1.48	14800	2.11	3.6	26	20	23	202	4	7	0.6	9.8	115	0.01
KL20-02	251.5	254.5	1.58	15800	2.57	3	32	17	20	334	2	12	0.01	8.5	94	0.01
KL20-02	254.5	257.5	1.22	12200	1.68	4.4	34	16	7	223	4	8	0.01	9.0	87	0.01
KL20-02	257.5	260.5	1.41	14100	2	3.1	39	12	5	63	2	12	0.01	8.4	99	0.01
KL20-02	260.5	263.5	1.09	10900	1.85	2	30	12	10	40	2	8	0.01	9.8	86	0.01
KL20-02	263.5	266.5	0.79	7900	1.19	2.3	36	12	23	21	1	11	0.01	9.0	95	0.01
KL20-02	266.5	269.5	1.36	13600	1.72	2.8	37	10	2	86	5	12	0.2	7.8	102	0.01
KL20-02	269.5	272.5	1.03	10300	1.85	2	49	15	11	61	2	8	0.8	9.9	88	0.01
KL20-02	272.5	275.5	1.09	10900	1.81	2.3	50	20	3	50	1	8	0.2	7.3	83	0.01
KL20-02	275.5	278.5	0.93	9300	1.44	2.3	29	12	6	17	1	7	0.01	6.8	101	0.01
KL20-02	278.5	281.5	1.28	12800	1.77	2.4	35	14	4	266	3	12	0.01	7.8	101	0.01
KL20-02	281.5	284.5	0.89	8900	1.3	1.3	39	10	4	52	2	8	0.2	5.8	115	0.01
KL20-02	284.5	287.5	0.94	9400	1.09	1.9	46	12	2	62	2	11	0.2	4.5	103	0.01
KL20-02	287.5	290.5	0.65	6500	0.66	2	41	19	8	118	2	7	0.7	4.8	99	0.01
KL20-02	290.5	293.5	0.52	5200	0.45	1.8	29	5	6	41	1	5	0.01	3.8	89	0.01
KL20-02	293.5	296.5	0.91	9100	0.97	2.4	47	7	2	73	1	13	0.01	3.8	91	0.01
KL20-02	296.5	299.5	1.07	10700	1.64	2.7	42	5	1	35	2	11	0.01	5.5	92	0.01
KL20-02	299.5	301	0.7	7000	0.96	2	47	8	2	99	1	9	0.01	3.5	92	0.01
KL20-02	301	304	0.87	8700	0.72	2.1	65	9	1	149	0.01	17	0.01	4.5	86	0.01
KL20-02	304	305.5	1.02	10200	1.1	2	63	8	2	59	1	17	0.2	4.3	85	0.01
KL20-02	305.5	308.5	0.95	9500	0.75	1.8	58	8	4	142	1	15	0.01	4.3	81	0.01
KL20-02	308.5	311.5	0.98	9800	0.58	3.7	128	32	150	217	1	13	3.7	4.5	66	0.01
KL20-02	311.5	313.4	1.08	10800	0.61	3.3	580	399	390	152	0.01	15	38	6.1	62	0.39
KL20-02	313.4	316	1.68	16800	1.15	2.7	70	17	10	56	1	19	0.7	4.8	83	0.01
KL20-02	316	318.5	1.19	11900	0.94	1.8	59	10	5	192	1	17	0.3	5.5	91	0.01
KL20-02	318.5	320.5	1.76	17600	1.99	3.4	64	6	4	174	1	16	0.5	7.0	86	0.01
KL20-02	320.5	323.5	1.38	13800	0.72	2.2	3200	1580	210	95	1	13	0.8	5.0	88	0.69
KL20-02	323.5	326.5	1.49	14900	0.77	2.4	185	44	26	108	2	14	0.5	4.8	56	0.01
KL20-02	326.5	329.5	1.42	14200	0.9	2.5	71	7	2	125	1	21	0.4	4.5	87	0.01
KL20-02	329.5	332	1.82	18200	0.79	2.7	79	19	50	56	2	15	3.1	6.0	74	0.01
KL20-02	332	333.6	1.48	14800	1.26	2.7	68	14	11	239	2	12	0.6	5.0	86	0.01
KL20-02	333.6	336.4	2.19	21900	1.35	3.1	88	9	3	138	0.01	18	0.5	4.5	107	0.01
KL20-02	336.4	338.5	1.61	16100	1.07	2.5	100	13	5	67	0.01	15	1	6.0	75	0.01
KL20-02	338.5	341.5	1.9	19000	1.26	1.8	137	16	21	78	0.01	17	2.5	8.8	70	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL20-02	341.5	344.5	0.83	8300	0.39	0.5	15	8	57	15	1	3	0.8	4.3	167	0.01
KL20-02	344.5	347.5	0.85	8500	0.37	1.3	53	58	240	13	3	4	1.5	4.3	171	0.01
KL20-02	347.5	350.5	2.5	25000	1.94	2.3	161	25	78	41	3	14	8.9	9.2	73	0.01
KL20-02	350.5	353.5	0.69	6900	0.37	1.5	95	58	70	84	1	7	1.5	4.3	137	0.01
KL20-02	353.5	356.5	0.27	2700	0.3	0.5	28	14	37	10	0.01	2	0.6	2.5	156	0.01
KL20-02	356.5	359.5	0.75	7500	0.4	1.3	47	25	100	5	4	2	2.5	5.7	186	0.01
KL20-02	359.5	362.5	0.44	4400	0.55	0.5	24	8	5	5	1	3	0.2	4.3	182	0.01
KL20-02	362.5	365.5	0.52	5200	0.37	1	46	23	4	25	1	7	0.01	3.5	143	0.01
KL20-02	365.5	367	0.57	5700	0.81	1	35	10	8	12	1	5	0.4	4.6	137	0.01
KL20-02	367	370	1.08	10800	1.69	2.4	20	10	1	18	4	5	0.2	5.3	166	0.01
KL20-02	370	373	0.96	9600	0.87	2.5	26	16	4	32	2	8	0.2	3.3	192	0.01
KL20-02	373	375.5	0.71	7100	0.47	2	34	12	64	28	3	4	0.9	3.3	208	0.01
KL20-02	375.5	377.5	0.58	5800	0.34	1	31	8	26	21	1	5	0.4	3.5	166	0.01
KL20-03	0	4	0.0113	113	0.01	1.7	540	356	9	5	0.01	3	2.3	2.3	21	0.01
KL20-03	4	7	0.0042	42	0.01	0.6	73	82	0.01	3	0.01	0.01	0.2	0.6	18	0.01
KL20-03	7	10	0.0082	82	0.01	0.7	90	77	1	2	0.01	2	0.3	1.4	23	0.01
KL20-03	10	13	0.007	70	0.03	1.5	247	322	11	0.01	0.01	0.01	0.9	2.3	27	0.01
KL20-03	13	16	0.0017	17	0.01	0.6	105	140	1	0.01	0.01	0.01	0.4	2.2	27	0.01
KL20-03	16	19	0.0085	85	0.01	0.7	271	114	1	3	0.01	0.01	0.3	1.8	31	0.01
KL20-03	19	21.5	0.0017	17	0.01	0.8	299	195	2	2	0.01	2	0.6	2.6	31	0.01
KL20-03	21.5	23.5	0.0075	75	0.01	1.1	138	87	1	0.01	0.01	0.01	0.6	0.9	31	0.01
KL20-03	23.5	27.5	0.0076	76	0.01	0.9	180	147	2	10	0.01	2	0.7	1.0	32	0.01
KL20-03	27.5	30.5	0.0027	27	0.01	1.8	370	367	4	4	0.01	0.01	0.7	2.9	30	0.01
KL20-03	30.5	33.4	0.0029	29	0.01	0.9	142	389	1	3	0.01	0.01	0.3	3.0	26	0.01
KL20-03	33.4	37	0.0015	15	0.01	1.5	240	206	3	6	0.01	0.01	0.4	3.0	20	0.01
KL20-03	37	40	0.0011	11	0.01	1.2	300	203	3	4	0.01	0.01	0.5	1.6	12	0.01
KL20-03	40	43	0.003	30	0.01	1.8	197	154	3	3	0.01	0.01	0.5	0.6	8	0.01
KL20-03	43	46	0.0014	14	0.01	1.4	204	160	4	5	0.01	0.01	0.4	1.5	15	0.01
KL20-03	46	49	0.0087	87	0.02	29.1	213	21	13	2	0.01	0.01	1	4.2	12	0.01
KL20-03	49	52	0.0057	57	0.03	14.8	490	198	7	2	0.01	2	0.9	6.2	13	0.01
KL20-03	52	55	0.0244	244	0.11	8.3	4590	1250	12	2	0.01	3	3.5	18.9	10	0.01
KL20-03	55	58	0.0085	85	0.04	3.4	640	228	7	7	0.01	0.01	0.8	3.8	17	0.01
KL20-03	58	61	0.0238	238	0.06	38.4	13300	17700	17	7	0.01	2	36	23.8	14	0.01
KL20-03	61	64	0.0279	279	0.01	22.5	3650	5600	36	8	0.01	0.01	8.2	20.5	20	0.01
KL20-03	64	67	0.019	190	0.01	17.6	1780	4950	18	14	0.01	0.01	7.3	12.3	20	0.01
KL20-03	67	70	0.0134	134	0.01	10	1780	3950	8	5	0.01	0.01	6.2	3.3	13	0.01
KL20-03	70	72.6	0.0082	82	0.01	7.5	2820	3380	4	3	0.01	0.01	3.5	4.3	13	0.01
KL20-03	72.6	74.1	0.011	110	0.01	5.5	410	3470	1	3	0.01	0.01	3.8	4.3	7	0.01
KL20-03	74.1	76	0.0231	231	0.01	10.3	5400	7500	6	6	0.01	2	9.8	5.8	22	0.01
KL20-03	76	79	0.0061	61	0.01	13.5	1680	1130	3	8	0.01	0.01	2.7	12.0	21	0.01
KL20-03	79	82	0.0245	245	0.02	5.9	241	740	13	11	0.01	0.01	1.6	4.7	14	0.01
KL20-03	82	85	0.0153	153	0.01	1.4	232	370	19	3	0.01	0.01	0.9	1.8	12	0.01
KL20-03	85	88	0.0204	204	0.01	6.8	1050	910	7	8	8	0.01	1.5	4.5	19	0.01
KL20-03	88	91	0.0177	177	0.01	2.8	960	1560	11	18	3	0.01	1.1	7.0	27	0.01
KL20-03	91	94	0.051	510	0.06	32.7	12000	9000	85	83	38	0.01	7.6	32.5	30	0.1
KL20-03	94	97	0.0203	203	0.04	11.5	4080	6300	8	10	0.01	0.01	8.3	5.3	22	0.01
KL20-03	97	100	0.0134	134	0.01	10.3	3260	8200	15	4	0.01	0.01	9.4	7.5	9	0.01
KL20-03	100	103	0.0079	79	0.03	18.8	2050	2790	7	16	0.01	2	7.3	8.0	13	0.01
KL20-03	103	105.5	0.0367	367	0.11	53.4	6800	8300	16	24	34	3	20.5	96.3	35	0.01
KL20-03	105.5	108.7	0.0102	102	0.01	7.5	3800	5450	9	6	1	0.01	5.6	6.3	20	0.01
KL20-03	108.7	111.8	0.0309	309	0.08	3.5	2100	2480	18	5	6	0.01	1.4	16.1	11	0.01
KL20-03	111.8	114.9	0.164	1640	0.54	43.2	20000	14700	34	15	128	6	2	114.0	12	0.01
KL20-03	114.9	118	0.31	3100	1.67	60.3	25000	4500	48	215	81	9	25.5	91.2	75	0.01
KL20-03	118	121	0.33	3300	1.52	2.7	430	320	23	276	4	7	1	11.3	46	0.01
KL20-03	121	124	0.32	3200	0.48	3.1	3100	203	35	206	10	9	1.1	7.0	41	0.13
KL20-03	124	127	0.74	7400	3.05	1.8	3870	53	18	17	80	16	0.7	16.3	24	0.01
KL20-03	127	129.5	0.61	6100	1.24	3.8	10200	33	4	118	324	8	0.3	20.2	6	0.01
KL20-03	129.5	132.5	0.625	6250	2.11	2.4	3000	49	5	218	322	10	0.01	17.3	70	0.01
KL20-03	132.5	134.5	0.159	1590	0.36	0.9	630	24	3	134	42	5	0.2	8.0	7	0.01
KL20-03	134.5	137.5	0.491	4910	0.79	1.5	460	29	4	283	12	9	0.01	6.7	0	0.01
KL20-03	137.5	140.5	0.84	8400	1.47	1.9	500	19	9	258	2	13	0.01	9.2	31	0.01
KL20-03	140.5	143.5	0.101	1010	0.35	0.7	129	11	15	104	2	6	0.01	2.5	10	0.01
KL20-03	143.5	146.5	0.67	6700	0.84	2.2	313	15	12	290	3	8	0.4	5.1	0	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL20-03	146.5	157	0.195	1950	0.82	1.2	177	33	22	242	2	7	0.3	4.8	27	0.01
KL20-03	157	163.9	0.336	3360	2.23	2.5	135	33	76	1170	0.01	9	2.8	13.0	31	0.01
KL20-03	163.9	166	0.292	2920	0.61	1	252	20	32	138	1	15	1.7	14.0	30	0.01
KL20-03	166	169	0.461	4610	0.67	1.9	373	23	28	62	0.01	14	0.3	8.5	42	0.01
KL20-03	169	172	0.458	4580	0.84	1.5	1390	28	39	365	7	21	0.5	11.5	29	0.01
KL20-03	172	175.5	1.02	10200	1.28	6	780	26	7	12	7	40	0.01	10.0	16	0.01
KL20-03	175.5	178	0.105	1050	0.06	1	2990	11	5	3	0.01	5	0.2	3.0	25	0.01
KL20-03	178	181	0.07	700	0.04	1.2	600	10	4	43	1	4	0.01	1.0	20	0.01
KL20-03	181	184	0.0394	394	0.04	0.9	450	50	2	0.01	0.01	3	0.01	0.0	10	0.01
KL20-03	184	187	0.053	530	0.03	0.01	324	8	3	0.01	0.01	4	0.01	1.0	8	0.01
KL20-03	187	190	0.0159	159	0.01	0.01	310	6	6	0.01	0.01	5	0.01	0.0	34	0.01
KL20-03	190	193	0.0206	206	0.01	0.01	670	6	7	0.01	0.01	3	0.01	0.0	6	0.01
KL20-03	193	196	0.0222	222	0.01	0.01	277	8	7	0.01	0.01	2	0.01	0.0	7	0.01
KL20-03	196	197.7	0.0042	42	0.01	0.01	205	17	8	0.01	0.01	3	0.01	0.0	10	0.01
KL20-03	197.7	202	1.03	10300	1.4	1.6	2250	14	7	19	0.01	75	0.01	16.2	46	0.01
KL20-03	202	205.8	1.54	15400	1.86	2.2	254	8	11	257	0.01	56	0.01	13.5	80	0.01
KL20-03	205.8	208	1.4	14000	1.08	1.6	148	12	2	1120	0.01	56	0.01	18.2	20	0.01
KL20-03	208	211	2.21	22100	1.96	3.2	156	11	4	790	0.01	64	0.01	17.5	43	0.01
KL20-03	211	212.5	1.06	10600	1.13	2.3	90	5	1	77	0.01	21	0.2	6.2	24	0.01
KL20-03	212.5	214.8	2.99	29900	3.24	5.5	176	9	3	133	0.01	100	0.01	16.2	56	0.01
KL20-03	214.8	217.8	0.49	4900	0.69	1	105	11	1	172	0.01	57	0.01	15.7	34	0.01
KL20-03	217.8	220.4	3.96	39600	21.2	5.7	87	12	4	24	2	58	0.01	18.7	46	0.01
KL20-03	220.4	221.9	2.89	28900	3.47	4.3	52	7	9	58	4	27	0.01	16.8	112	0.01
KL20-03	221.9	224.9	1.16	11600	0.76	3.1	137	475	39	111	0.01	8	0.5	6.0	100	0.01
KL20-03	224.9	226.7	2.36	23600	4.1	7.4	32	13	1	27	9	12	0.01	30.0	74	0.01
KL20-03	226.7	229	1.7	17000	2.38	3.4	32	7	2	69	3	12	0.01	16.0	106	0.01
KL20-03	229	232	1.45	14500	1.92	2.3	29	0.01	1	125	0.01	9	0.01	11.5	117	0.01
KL20-03	232	235	0.67	6700	1.04	1.8	30	0.01	2	122	0.01	9	0.01	7.0	92	0.01
KL20-03	235	238	1.31	13100	1.34	2.7	26	0.01	3	283	0.01	8	0.01	10.5	71	0.01
KL20-03	238	240.5	0.125	1250	0.01	0.6	134	26	16	2	0.01	5	0.01	0.0	37	0.01
KL20-03	240.5	243.5	1.33	13300	1.72	2.4	32	7	1	113	0.01	10	0.01	12.5	71	0.01
KL20-03	243.5	246.5	1.43	14300	2.52	3.9	21	13	0.01	183	5	8	0.01	9.0	109	0.01
KL20-03	246.5	249.6	1.34	13400	1.48	4.3	22	0.01	0.01	131	2	8	0.01	10.0	105	0.01
KL20-03	249.6	252.7	1.55	15500	1.81	2.1	22	11	3	173	1	10	0.01	10.1	91	0.01
KL20-03	252.7	256	1.43	14300	1.52	2.1	30	15	1	200	2	16	0.5	9.0	90	0.01
KL20-03	256	259	1.09	10900	1.08	1.8	32	10	0.01	237	1	6	0.3	8.5	109	0.01
KL20-03	259	262	1.19	11900	1.81	1.2	30	9	1	327	1	7	0.01	7.0	76	0.01
KL20-03	262	265	1.18	11800	0.43	2.1	28	9	5	238	3	10	0.4	10.0	88	0.01
KL20-03	265	268	0.71	7100	1.03	0.7	18	5	0.01	130	1	7	0.5	5.0	51	0.01
KL20-03	268	271	0.95	9500	1.23	1.8	33	7	3	166	1	10	0.6	7.2	70	0.01
KL20-03	271	274	1.01	10100	1.28	1.9	27	10	3	172	2	8	0.01	10.0	56	0.01
KL20-03	274	277	1.41	14100	1.24	2.3	56	30	2	205	1	10	0.01	10.5	76	0.01
KL20-03	277	280	0.71	7100	0.72	1.1	37	6	3	300	0.01	6	0.01	5.6	82	0.01
KL20-03	280	283	0.75	7500	0.69	1.3	44	6	1	230	0.01	12	0.2	7.4	91	0.01
KL20-03	283	286.1	1.05	10500	0.65	1.6	40	8	2	320	0.01	13	0.01	8.5	88	0.01
KL20-03	286.1	289	1.01	10100	0.51	1.6	50	0.01	1	82	0.01	15	0.01	6.8	76	0.01
KL20-03	289	292	1.02	10200	0.49	1.9	43	0.01	0.01	251	0.01	19	0.01	9.5	74	0.01
KL20-03	292	294.1	0.83	8300	0.49	1.1	42	8	2	71	0.01	12	0.01	10.5	94	0.01
KL20-03	294.1	296	0.78	7800	0.81	1.2	39	0.01	1	141	0.01	13	0.01	5.0	82	0.01
KL20-03	296	298	0.438	4380	0.25	0.8	40	0.01	0.01	84	0.01	10	0.01	8.3	39	0.01
KL20-03	298	301	0.498	4980	0.25	1	46	0.01	0.01	114	0.01	13	0.01	7.5	43	0.01
KL20-03	301	304	0.499	4990	0.35	1	24	6	2	110	0.01	12	0.01	8.5	46	0.01
KL20-03	304	307.2	0.63	6300	0.51	1.2	33	10	7	230	0.01	9	0.01	7.3	50	0.01
KL20-03	307.2	310	0.85	8500	0.5	1.4	261	127	340	122	0.01	9	0.7	9.5	77	0.45
KL20-03	310	313	0.411	4110	0.25	0.8	18	0.01	13	110	0.01	10	0.3	6.8	76	0.12
KL20-03	313	316	0.93	9300	0.26	2.1	106	16	660	156	0.01	12	1.9	10.3	64	6.52
KL20-03	316	317.7	1.43	14300	0.8	2	39	7	180	270	0.01	13	0.4	14.0	83	0.38
KL20-03	317.7	320.5	1.14	11400	1.05	1.7	105	9	12	920	0.01	20	0.01	17.5	111	0.01
KL20-03	320.5	323.5	1.64	16400	1.52	3	121	7	14	278	0.01	30	0.01	13.0	74	0.01
KL20-03	323.5	325.7	0.78	7800	0.73	1.7	72	6	2	260	0.01	21	0.01	19.3	86	0.01
KL20-03	325.7	328	1.14	11400	0.67	2	43	7	15	1600	0.01	15	0.01	11.8	50	0.01
KL20-03	328	331	1.18	11800	0.83	1.8	50	8	1	1800	0.01	16	0.01	9.0	37	0.01
KL20-03	331	334	0.83	8300	0.59	1.4	34	0.01	0.01	1200	0.01	15	0.01	9.3	42	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL20-03	334	337	1.38	13800	1.19	1.8	63	0.01	0.01	1600	0.01	18	0.01	12.0	27	0.01
KL20-03	337	340	1.18	11800	0.97	1.6	53	7	0.01	1200	0.01	19	0.01	11.3	28	0.01
KL20-03	340	343	1.28	12800	0.77	1.7	47	8	2	580	0.01	16	0.01	9.0	35	0.01
KL20-03	343	344.5	0.89	8900	0.51	1.8	58	6	0.01	1100	0.01	12	0.01	8.4	41	0.01
KL20-03	344.5	346.2	2.19	21900	0.86	3	83	6	2	2700	0.01	18	0.01	15.0	28	0.01
KL20-03	346.2	349	1.55	15500	0.59	3.3	84	13	11	2740	0.01	17	0.01	13.0	46	0.01
KL20-03	349	352	0.54	5400	0.22	1.4	97	12	9	4100	1	18	0.01	10.2	97	0.01
KL20-03	352	355	1.01	10100	0.79	2.6	112	26	4	3500	0.01	16	0.01	13.0	73	0.01
KL20-03	355	358	1.28	12800	0.46	6.5	90	28	14	1600	0.01	37	0.01	13.8	65	0.01
KL20-03	358	361	1.15	11500	0.14	4.8	72	30	18	3000	1	40	0.01	22.1	62	0.01
KL20-03	361	364	0.82	8200	0.25	3.8	78	25	11	1300	1	14	0.01	11.5	42	0.01
KL20-03	364	366	0.58	5800	0.32	3	51	12	17	1900	1	10	0.01	9.0	43	0.01
KL20-03	366	367.5	0.245	2450	0.2	1.8	53	32	24	1700	1	31	0.01	20.0	46	0.01
KL20-03	367.5	370	2.68	26800	1.56	21.8	510	48	24	55	6	158	0.01	24.5	64	0.01
KL20-03	370	373	1.58	15800	1.12	10.8	209	22	17	97	2	125	0.01	51.9	81	0.01
KL20-03	373	376	1.13	11300	1.17	6.5	138	24	15	340	0.01	32	0.01	25.8	111	0.01
KL20-03	376	379	0.54	5400	0.5	3.7	151	56	25	250	1	36	0.01	23.8	30	0.01
KL20-03	379	382	0.53	5300	0.49	1.6	141	20	7	46	0.01	14	0.01	7.8	46	0.01
KL20-03	382	385	0.92	9200	0.73	2.2	123	13	13	10	0.01	19	0.01	9.3	41	0.01
KL20-03	385	388	1.78	17800	1.71	3.4	164	14	3	92	0.01	41	0.01	16.0	54	0.01
KL20-03	388	391	2.92	29200	2.01	5	221	13	13	61	0.01	47	0.01	26.9	57	0.01
KL20-03	391	394	1.13	11300	1.21	1.9	110	9	7	0.01	0.01	18	0.01	11.0	55	0.01
KL20-03	394	397	0.96	9600	0.87	1.4	118	11	5	9	0.01	16	0.01	6.8	101	0.01
KL20-03	397	400	0.433	4330	0.62	0.8	78	10	12	1100	0.01	12	0.01	6.3	70	0.01
KL20-03	400	403	0.64	6400	0.78	1.1	57	8	19	2200	0.01	11	0.01	8.8	61	0.01
KL20-03	403	406	0.363	3630	0.48	0.8	49	8	20	4200	0.01	6	0.01	9.5	62	0.01
KL20-03	406	409	0.403	4030	0.54	1	50	7	23	2300	0.01	19	0.01	5.8	57	0.01
KL20-03	409	412	0.315	3150	0.39	1	45	7	14	1540	0.01	37	0.01	6.5	56	0.01
KL20-03	412	415	1.21	12100	1.32	3.8	149	11	25	2400	1	79	0.01	9.8	73	0.01
KL20-03	415	418	0.97	9700	1.12	4.5	117	8	27	930	0.01	90	0.01	7.0	59	0.01
KL20-03	418	420.6	1.14	11400	1.64	5.8	140	14	27	1770	0.01	70	0.01	7.3	76	0.01
KL20-03	420.6	423	0.54	5400	1.04	1.9	78	14	27	490	0.01	30	0.01	9.0	64	0.01
KL20-03	423	425.3	0.65	6500	1	1.4	67	11	30	220	0.01	14	0.01	6.3	74	0.01
KL20-03	425.3	427.5	0.89	8900	0.82	1.3	103	19	12	1620	0.01	16	0.01	10.8	80	0.01
KL20-03	427.5	429.9	1.52	15200	2.42	5.5	132	18	4	360	0.01	58	0.01	9.0	96	0.01
KL20-03	429.9	433	2.15	21500	2.77	4.9	239	14	2	40	0.01	53	0.5	12.0	40	0.01
KL20-03	433	435.2	2.2	22000	1.92	6.3	290	18	0.01	28	0.01	57	0.01	16.0	42	0.01
KL20-03	435.2	437.2	6.06	60600	4.28	19.3	510	10	4	27	0.01	98	0.01	32.5	40	0.01
KL20-03	437.2	439	6.78	67800	5	17.8	470	13	4	7	0.01	146	0.01	17.5	30	0.01
KL20-03	439	442	1.39	13900	2.22	8	283	25	1	40	0.01	122	0.01	13.2	41	0.01
KL20-03	442	445	1.72	17200	1.33	9.3	352	18	26	30	0.01	124	0.01	14.0	65	0.01
KL20-03	445	448	1.09	10900	0.62	6	127	16	43	320	0.01	82	0.01	8.5	83	0.01
KL20-03	448	450.2	0.325	3250	2.37	1.7	80	14	11	420	0.01	11	0.01	13.0	83	0.01
KL20-03	450.2	452.5	0.142	1420	0.17	0.8	42	12	7	130	0.01	8	0.01	2.7	107	0.01
KL20-03	452.5	454	0.15	1500	1.19	0.5	37	11	2	140	0.01	2	0.01	1.3	187	0.01
KL20-03	454	456.3	0.171	1710	0.2	0.5	61	23	6	490	0.01	7	0.01	1.9	99	0.01
KL20-03	456.3	458.5	0.123	1230	0.13	0.01	35	7	1	460	0.01	3	0.5	1.0	126	0.01
KL20-03	458.5	460.4	0.146	1460	0.14	0.01	34	8	3	110	0.01	9	0.01	2.0	52	0.01
KL20-03	460.4	463.6	0.191	1910	0.21	0.8	60	10	2	57	0.01	11	0.01	2.6	43	0.01
KL20-03	463.6	465.5	0.505	5050	0.45	1.4	88	20	4	58	0.01	18	0.01	5.3	58	0.01
KL20-03	465.5	467.5	0.364	3640	0.37	1.3	73	12	6	580	0.01	9	0.01	4.3	41	0.01
KL20-03	467.5	470.5	0.216	2160	0.3	1.1	28	10	22	500	1	2	0.01	2.8	47	0.01
KL20-03	470.5	473.5	0.326	3260	0.35	1.1	32	13	16	107	0.01	4	0.01	5.2	24	0.01
KL20-03	473.5	476.6	0.272	2720	0.24	1.3	55	24	6	72	1	3	0.01	3.3	41	0.01
KL20-03	476.6	478.4	0.078	780	0.12	0.5	64	17	9	3600	2	4	0.01	3.3	23	0.01
KL20-03	478.4	480.1	2.83	28300	1.89	7.8	550	26	32	40	1	56	0.01	19.4	49	0.01
KL20-03	480.1	482.1	2.26	22600	1.7	7.3	5600	28	19	15	1	90	0.01	10.9	27	0.01
KL20-03	482.1	483.8	0.0227	227	0.02	0.01	600	6	3	0.01	0.01	0.01	0.01	1.0	18	0.01
KL20-03	483.8	485.8	0.0038	38	0.01	0.01	9	7	0.01	3	0.01	0.01	0.01	1.8	16	0.01
KL20-03	485.8	487.8	0.0232	232	0.01	0.01	65	6	1	0.01	0.01	0.01	0.01	0.0	16	0.01
KL20-03	487.8	490.9	0.0075	75	0.01	0.01	19	6	1	0.01	0.01	0.01	0.01	1.8	20	0.01
KL20-03	490.9	493.9	0.0091	91	0.01	0.01	20	7	2	0.01	0.01	0.01	0.01	0.5	17	0.01
KL20-03	493.9	495.8	0.0021	21	0.01	0.01	19	10	0.01	2	0.01	0.01	0.01	1.0	21	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL20-03	495.8	497.5	0.0027		27	0.01	0.9	306	64	2	4	0.01	0.01	0.7	2.2	18	0.01
KL20-03	497.5	500.5	0.001		10	0.01	0.01	43	14	3	3	0.01	0.01	0.01	1.0	18	0.01
KL20-03	500.5	503.5	0.0005		5	0.01	0.01	15	8	1	2	0.01	0.01	0.01	0.7	18	0.01
KL20-03	503.5	506.5	0.0027		27	0.01	0.01	26	7	3	6	0.01	0.01	0.5	0.7	17	0.01
KL20-03	506.5	509.5	0.001		10	0.01	0.01	16	7	1	3	0.01	0.01	0.01	0.7	16	0.01
KL20-03	509.5	512.5	0.0015		15	0.01	0.01	13	8	0.01	2	0.01	2	0.01	0.0	24	0.01
KL20-03	512.5	515.5	0.0031		31	0.01	0.01	46	6	2	5	0.01	0.01	0.01	0.0	17	0.01
KL20-03	515.5	518.5	0.0035		35	0.01	0.01	16	7	1	6	0.01	0.01	0.01	0.7	24	0.01
KL20-03	518.5	521.5	0.0018		18	0.01	0.01	10	6	0.01	5	0.01	0.01	0.01	0.5	16	0.01
KL20-03	521.5	524.5	0.0012		12	0.01	0.01	28	12	0.01	3	0.01	0.01	0.01	0.7	17	0.01
KL20-03	524.5	527.5	0.001		10	0.01	0.01	16	7	0.01	9	0.01	0.01	0.01	0.6	21	0.01
KL20-03	527.5	530.5	0.0086		86	0.01	0.01	15	20	4	7	0.01	2	0.01	1.1	15	0.01
KL20-03	530.5	533.5	0.0012		12	0.01	0.01	48	14	0.01	5	0.01	0.01	0.01	1.0	17	0.01
KL20-03	533.5	536.2	0.0012		12	0.01	0.01	15	12	0.01	4	0.01	0.01	0.01	0.0	18	0.01
KL20-03	536.2	538	0.0005		5	0.01	0.01	5	6	0.01	3	0.01	0.01	0.01	0.0	13	0.01
KL20-04	0	2.9	0.0039		39	0.06	3.1	236	77	9	24	0.01	0.01	2.2	1.9	21	0.01
KL20-04	2.9	6	0.0018		18	0.01	0.8	169	72	4	6	0.01	0.01	0.6	1.3	19	0.01
KL20-04	6	8.8	0.0015		15	0.01	0.6	88	46	2	5	0.01	0.01	0.8	0.0	21	0.01
KL20-04	8.8	12	0.0009		9	0.01	0.8	212	145	4	4	0.01	0.01	0.8	2.4	22	0.01
KL20-04	12	14.5	0.0034		34	0.01	1	500	312	15	3	0.01	0.01	1.3	1.1	25	0.01
KL20-04	14.5	17.5	0.0014		14	0.01	0.01	102	63	2	3	0.01	0.01	0.01	0.9	23	0.01
KL20-04	17.5	20.5	0.0068		68	0.01	1	790	460	16	2	0.01	0.01	6.9	1.2	28	0.01
KL20-04	20.5	22	0.0016		16	0.01	0.01	86	111	4	4	0.01	0.01	0.9	0.0	29	0.01
KL20-04	22	25	0.001		10	0.02	1.2	274	980	3	6	0.01	0.01	1	1.9	26	0.01
KL20-04	25	28	0.0013		13	0.02	2.6	800	830	6	3	0.01	0.01	0.01	2.0	38	0.01
KL20-04	28	31	0.0007		7	0.01	0.01	246	208	2	8	0.01	0.01	0.01	0.0	30	0.01
KL20-04	31	34	0.0013		13	0.01	0.8	810	460	2	4	0.01	0.01	1	1.8	31	0.01
KL20-04	34	35.5	0.0041		41	0.01	8.1	3270	3050	8	15	0.01	0.01	3.9	10.0	23	0.01
KL20-04	35.5	38.5	0.0008		8	0.01	3.2	328	211	11	16	0.01	0.01	0.5	1.0	13	0.01
KL20-04	38.5	43	0.0018		18	0.01	25.9	810	630	14	10	0.01	0.01	4.7	2.9	7	0.01
KL20-04	43	46	0.169		1690	0.7	62	25600	16300	840	8	0.01	0.01	50	16.0	14	0.63
KL20-04	46	49	0.0134		134	0.04	6.5	2110	1310	52	4	0.01	0.01	5	2.8	16	0.01
KL20-04	49	52	0.003		30	0.01	12.2	379	213	15	7	0.01	0.01	2.6	2.2	8	0.01
KL20-04	52	55	0.0013		13	0.01	2.2	238	166	9	4	0.01	0.01	1.1	1.5	8	0.01
KL20-04	55	58	0.0019		19	0.01	2.6	359	298	13	8	0.01	0.01	1.4	7.2	12	0.01
KL20-04	58	61	0.018		180	0.15	59	15200	14500	42	5	0.01	0.01	40	26.4	15	0.01
KL20-04	61	64	0.0061		61	0.06	50	4800	6600	16	3	0.01	0.01	14.4	33.0	13	0.01
KL20-04	64	67	0.0013		13	0.02	4.9	720	1530	10	0.01	0.01	0.01	2	5.0	10	0.01
KL20-04	67	70	0.003		30	0.03	11.9	2780	4220	23	7	0.01	0.01	5.4	6.6	19	0.01
KL20-04	70	73	0.0034		34	0.03	6.8	1120	3200	12	4	0.01	0.01	3	12.3	20	0.01
KL20-04	73	76	0.0028		28	0.01	9.5	416	6700	4	3	0.01	0.01	6.8	16.4	14	0.01
KL20-04	76	79	0.0022		22	0.01	1.6	510	1120	6	7	0.01	0.01	0.6	4.9	9	0.01
KL20-04	79	82	0.0029		29	0.01	2.1	1330	760	12	6	0.01	0.01	1	3.8	11	0.01
KL20-04	82	85	0.0048		48	0.01	1.8	420	590	14	20	0.01	0.01	0.7	2.6	7	0.01
KL20-04	85	88	0.0076		76	0.01	1.3	409	690	15	24	2	0.01	0.01	3.3	13	0.01
KL20-04	88	89.2	0.0096		96	0.03	0.01	460	249	12	5	0.01	0.01	0.01	3.0	10	0.01
KL20-04	89.2	91	0.0097		97	0.03	5.3	1780	3820	18	9	2	0.01	2.6	17.5	11	0.01
KL20-04	91	94	0.58		5800	0.95	11.2	3070	3000	12	41	40	21	0.9	59.5	32	0.01
KL20-04	94	97	0.57		5700	0.73	60	20100	97200	13	149	130	14	10.3	663.0	42	0.01
KL20-04	97	100	0.498		4980	0.72	15.5	3770	2300	38	9	57	18	1.3	97.0	32	0.01
KL20-04	100	103	0.093		930	0.42	2	1610	213	11	3	0.01	4	0.4	7.1	21	0.01
KL20-04	103	106	0.05		500	0.28	2.4	1330	520	27	6	1	2	0.7	6.1	19	0.01
KL20-04	106	109	0.0329		329	0.16	2.1	1670	570	11	6	8	2	0.6	10.0	24	0.01
KL20-04	109	112	0.054		540	0.13	5.2	3060	1410	10	2	23	3	1.3	14.0	29	0.01
KL20-04	112	115	0.051		510	0.13	1.6	4820	360	8	0.01	40	4	0.8	17.7	19	0.01
KL20-04	115	118	0.154		1540	0.46	8.3	6800	8100	13	26	22	8	0.6	65.0	25	0.01
KL20-04	118	121	0.6		6000	1.19	15.2	12700	2500	33	26	56	32	5.2	82.0	26	0.01
KL20-04	121	124	1.73		17300	2.71	44	16000	5000	42	260	160	24	4.6	79.8	63	0.01
KL20-04	124	127	0.282		2820	0.85	3.5	470	160	140	800	1	8	3.4	12.6	36	0.01
KL20-04	127	130	0.222		2220	0.72	2.3	204	113	20	395	0.01	9	6.2	6.5	40	0.01
KL20-04	130	133	0.299		2990	0.95	2.1	590	78	130	149	11	14	8.1	13.4	23	0.01
KL20-04	133	136	1.11		11100	3.53	2.3	2100	120	19	134	36	19	0.9	15.6	26	0.01
KL20-04	136	139	0.316		3160	0.86	0.9	148	40	23	270	1	10	0.8	21.5	46	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL20-04	139	142	0.95	9500	1.03	2.1	885	21	19	234	2	20	0.3	19.0	53	0.01
KL20-04	142	145	1.19	11900	0.84	38	30800	2900	2860	340	10	11	10	11.0	47	2.99
KL20-04	145	148	0.74	7400	0.85	2	670	47	38	359	3	14	1.8	8.1	35	0.01
KL20-04	148	151	0.202	2020	0.56	1.1	125	19	19	213	1	6	1	5.8	60	0.01
KL20-04	151	154	0.4	4000	0.97	9	6200	1180	170	470	1	11	7.3	10.0	57	0.33
KL20-04	154	157	0.117	1170	0.83	3.7	1440	280	140	220	3	8	12.3	7.7	68	0.17
KL20-04	157	160	0.244	2440	0.88	1.4	154	39	14	444	2	10	1.7	17.7	76	0.01
KL20-04	160	163	0.58	5800	1.46	1.9	440	13	39	157	2	13	4	32.5	46	0.01
KL20-04	163	166	0.058	580	0.15	0.01	88	15	3	2700	1	10	4.3	8.4	22	0.01
KL20-04	166	169	0.058	580	0.4	0.7	58	14	28	1500	0.01	9	0.01	8.3	53	0.01
KL20-04	169	172	0.047	470	8.42	21	270	34	62	775	1	10	11.8	5.1	96	0.13
KL20-04	172	175	1.4	14000	1.27	4.4	2000	19	5	30	0.01	66	0.01	25.5	70	0.01
KL20-04	175	178	1.02	10200	0.65	2.8	450	64	22	61	0.01	53	0.01	13.3	53	0.01
KL20-04	178	181	1.83	18300	1.09	1.8	236	43	0.01	63	0.01	55	0.01	25.5	42	0.01
KL20-04	181	185.2	1.07	10700	0.9	1.3	1090	120	15	28	2	37	0.7	15.5	35	0.01
KL20-04	185.2	190	2	20000	1.58	1.7	234	18	0.01	8	0.01	43	0.01	26.0	14	0.01
KL20-04	190	193	2.42	24200	1.75	2.8	258	14	0.01	2	0.01	56	0.01	26.9	16	0.01
KL20-04	193	197.5	1.68	16800	1.16	2	239	10	7	142	0.01	42	0.01	24.0	34	0.01
KL20-04	197.5	200.5	4.1	41000	2.13	3.4	164	7	0.01	165	0.01	51	0.01	28.8	28	0.01
KL20-04	200.5	203.5	0.925	9250	0.4	1.6	152	17	0.01	147	0.01	57	0.01	29.0	42	0.01
KL20-04	203.5	206.5	0.7	7000	0.28	2.7	114	91	1	66	0.01	57	0.2	19.2	29	0.01
KL20-04	206.5	209.5	1.74	17400	1.08	2.9	180	11	0.01	68	0.01	29	0.01	12.5	27	0.01
KL20-04	209.5	212.5	1.05	10500	0.76	1	114	8	0.01	76	0.01	51	0.01	25.3	38	0.01
KL20-04	212.5	215.5	1.35	13500	0.97	1.6	96	5	0.01	27	3	46	0.3	8.7	54	0.01
KL20-04	215.5	218.5	4.88	48800	1.63	10.5	98	9	0.01	5	2	54	0.01	8.4	50	0.01
KL20-04	218.5	221	1.45	14500	0.75	4.8	25	6	0.01	138	1	9	0.4	4.0	63	0.01
KL20-04	221	223.7	1.5	15000	0.87	8.6	22	5	1	163	0.01	8	0.2	3.1	51	0.01
KL20-04	223.7	226	1.7	17000	0.88	3.8	84	52	3	64	1	16	0.01	10.6	63	0.01
KL20-04	226	229	1.71	17100	1.57	2.5	31	9	0.01	84	3	11	0.01	11.9	106	0.01
KL20-04	229	232	1.24	12400	1.92	2.6	17	5	18	88	3	8	0.2	12.0	49	0.01
KL20-04	232	235	0.77	7700	1.29	2.1	31	6	5	63	0.01	7	0.01	5.8	45	0.01
KL20-04	235	238	0.93	9300	0.9	1.5	50	9	0.01	103	0.01	8	0.01	8.0	70	0.01
KL20-04	238	241	1.41	14100	1.51	3.2	28	5	0.01	203	2	12	0.01	16.3	62	0.01
KL20-04	241	244	1.5	15000	1.5	4.5	23	8	0.01	116	4	10	0.01	16.3	50	0.01
KL20-04	244	247	1.8	18000	1.95	4.7	35	6	0.01	107	5	10	0.01	13.5	105	0.01
KL20-04	247	250	1.52	15200	1.65	4	42	20	16	32	9	10	0.7	19.0	86	0.01
KL20-04	250	253	1.45	14500	2.02	3.4	28	14	2	37	7	8	0.01	14.0	73	0.01
KL20-04	253	256	1.21	12100	0.72	1.8	63	20	12	129	0.01	7	0.01	11.5	84	0.01
KL20-04	256	259	1.13	11300	0.65	1.1	37	14	1	51	0.01	5	0.01	8.0	75	0.01
KL20-04	259	262	1.25	12500	0.94	1.3	39	13	1	55	1	7	0.01	11.0	77	0.01
KL20-04	262	265	0.011	110	0.01	0.01	61	25	2	3	0.01	15	0.01	0.0	20	0.01
KL20-04	265	268	1.8	18000	1.14	3.6	56	12	2	65	2	14	0.01	6.7	81	0.01
KL20-04	268	271	1.34	13400	0.75	2.4	36	10	2	114	0.01	12	0.01	11.7	69	0.01
KL20-04	271	274	1.07	10700	0.65	1.4	31	16	2	273	0.01	10	0.01	12.5	30	0.01
KL20-04	274	275.5	1.84	18400	1.06	3.9	42	17	10	240	1	15	0.01	16.5	63	0.01
KL20-04	275.5	278	1.75	17500	1.35	3.5	41	16	19	289	0.01	10	0.01	6.5	32	0.01
KL20-04	278	279.1	2.13	21300	1.32	2.4	64	15	23	171	1	38	0.01	11.2	172	0.01
KL20-04	279.1	281.5	1.26	12600	1.15	1.8	94	12	94	148	1	14	0.01	6.4	31	0.01
KL20-04	281.5	284.5	1.16	11600	0.77	2	50	14	22	400	0.01	10	0.9	8.5	26	0.01
KL20-04	284.5	286.4	0.74	7400	0.35	1.2	32	7	27	720	0.01	7	0.01	4.2	29	0.01
KL20-04	286.4	288.5	0.75	7500	0.41	1.4	27	8	12	303	0.01	7	0.4	4.4	51	0.01
KL20-04	288.5	290.5	1.47	14700	0.59	2.6	40	15	4	1020	0.01	10	0.6	3.0	25	0.01
KL20-04	290.5	292.9	2.26	22600	1.05	4.2	57	13	9	1300	0.01	17	0.5	8.8	31	0.01
KL20-04	292.9	295	2.85	28500	1.78	11.2	294	11	40	1370	2	126	0.01	12.5	125	0.01
KL20-04	295	298	1.77	17700	2	17.1	25900	24	52	123	13	96	0.01	35.3	150	0.01
KL20-04	298	301	0.48	4800	1.36	4.9	14900	54	76	8	62	63	0.01	102.0	150	0.01
KL20-04	301	304	0.495	4950	2.2	5.3	830	40	100	21	15	85	0.01	9.4	128	0.01
KL20-04	304	307	0.72	7200	0.68	5.1	1200	36	17	36	9	92	0.2	31.1	95	0.01
KL20-04	307	310	2.24	22400	1.3	14	359	18	9	107	40	56	0.01	31.0	151	0.01
KL20-04	310	313	2.06	20600	3.22	15.1	367	43	87	53	11	25	0.01	6.5	90	0.01
KL20-04	313	315.2	0.386	3860	1.42	2	720	10	36	34	2	66	0.01	13.0	53	0.01
KL20-04	315.2	316.5	0.323	3230	0.63	0.01	420	8	6	15	0.01	54	0.01	7.4	56	0.01
KL20-04	316.5	319.3	0.288	2880	0.9	0.01	3750	11	10	14	13	63	0.01	7.4	40	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL20-04	319.3	320.5	0.66	6600	0.5	0.01	660	10	8	117	0.01	9	0.01	6.3	32	0.01
KL20-04	320.5	323.4	0.155	1550	1.53	1.5	14400	21	34	12	14	76	0.01	8.6	30	0.01
KL20-04	323.4	325.5	0.404	4040	0.3	3.4	890	40	26	18	1	19	0.01	6.5	47	0.01
KL20-04	325.5	328.5	1.19	11900	1.37	4.4	500	81	50	8	1	28	0.01	6.5	51	0.01
KL20-04	328.5	331.5	0.324	3240	0.37	0.01	87	25	71	8	0.01	7	0.01	5.5	57	0.01
KL20-04	331.5	334.5	0.054	540	1.67	0.01	46	18	34	5	0.01	3	0.01	0.9	60	0.01
KL20-04	334.5	336.5	0.0173	173	0.65	0.01	26	16	29	15	0.01	2	0.01	0.9	45	0.01
KL20-04	336.5	338.6	0.0136	136	0.17	0.01	22	13	33	17	0.01	2	0.01	0.0	43	0.01
KL20-04	338.6	340.5	0.0084	84	0.08	0.01	18	14	26	26	0.01	2	0.01	0.0	54	0.01
KL20-04	340.5	343.5	0.0044	44	0.1	0.01	25	15	25	21	0.01	2	0.01	0.0	55	0.01
KL20-04	343.5	346.5	0.0036	36	0.06	0.01	33	18	15	15	0.01	3	0.2	0.8	50	0.01
KL20-04	346.5	349.5	0.0032	32	0.03	0.01	40	19	11	3670	0.01	3	0.2	4.0	65	0.01
KL20-04	349.5	351.5	0.223	2230	0.08	0.01	41	20	7	2320	0.01	3	0.01	3.5	47	0.01
KL20-04	351.5	353.3	0.185	1850	0.21	0.01	36	19	14	870	0.01	2	0.01	2.0	64	0.01
KL20-04	353.3	354.2	15.3	153000	13.2	17.3	610	18	8	94	6	122	0.01	7.5	52	0.01
KL20-04	354.2	356	0.101	1010	0.08	0.01	40	7	9	83	0.01	5	0.01	0.5	100	0.01
KL20-04	356	358	0.0351	351	0.09	0.01	27	11	18	1370	0.01	4	0.01	2.0	75	0.01
KL20-04	358	360.8	0.0182	182	0.09	0.01	31	18	18	4360	0.01	3	0.01	6.0	70	0.01
KL20-04	360.8	363.3	0.423	4230	0.46	0.01	21	14	16	58	6	3	0.01	6.7	48	0.01
KL20-04	363.3	366.5	1.61	16100	1.33	2	33	14	30	104	0.01	18	0.01	5.4	56	0.01
KL20-04	366.5	369.5	0.71	7100	2.05	2	20	76	20	30	120	3	0.2	9.3	50	0.01
KL20-04	369.5	372.5	0.0122	122	0.09	0.01	17	18	20	43	0.01	3	0.6	0.0	58	0.01
KL20-04	372.5	375.5	0.115	1150	0.1	0.01	30	23	21	272	0.01	2	0.3	1.2	67	0.01
KL20-04	375.5	378.5	0.294	2940	0.16	1.3	121	35	12	1460	1	4	0.2	4.8	74	0.01
KL20-04	378.5	380.3	1.65	16500	0.81	4.8	239	89	38	540	0.01	13	0.3	11.3	81	0.01
KL20-04	380.3	382.5	0.89	8900	0.65	2.3	113	36	32	115	1	5	0.01	7.4	57	0.01
KL20-04	382.5	385.5	2.21	22100	1.75	5.2	135	56	58	117	3	15	0.01	15.5	78	0.01
KL20-04	385.5	387.8	0.85	8500	1.06	2.3	73	38	51	32	1	10	0.01	11.6	63	0.01
KL20-04	387.8	389.1	5.25	52500	4.12	12.5	402	54	73	11	2	114	0.01	21.0	66	0.01
KL20-04	389.1	391.5	2.24	22400	2	4.7	320	26	31	3	0.01	107	0.01	6.0	43	0.01
KL20-04	391.5	393.9	1.41	14100	1.05	4.5	151	73	78	11	0.01	34	0.01	12.5	55	0.01
KL20-04	393.9	395.5	1.63	16300	1.67	4.8	269	56	30	52	0.01	51	0.3	13.2	58	0.01
KL20-04	395.5	397.5	0.237	2370	0.21	0.01	106	83	89	2	0.01	4	0.01	3.2	56	0.01
KL20-04	397.5	400.5	0.116	1160	0.08	0.01	27	22	26	6	0.01	4	0.01	1.2	57	0.01
KL20-04	400.5	403.5	0.248	2480	0.15	1.3	28	32	33	9	1	4	0.01	3.6	61	0.01
KL20-04	403.5	406.5	0.71	7100	0.47	2.4	156	47	62	18	0.01	4	0.01	6.8	62	0.01
KL20-04	406.5	409.5	0.83	8300	0.58	3.6	161	123	50	330	1	7	0.01	11.6	108	0.01
KL20-04	409.5	412.5	0.212	2120	0.13	0.01	349	18	24	183	0.01	6	0.2	9.5	152	0.01
KL20-04	412.5	415.5	0.54	5400	0.41	2.4	295	141	47	21	1	8	0.2	7.0	80	0.01
KL20-04	415.5	417.5	1.2	12000	0.54	5	530	204	65	90	1	24	0.4	12.0	65	0.01
KL20-04	417.5	419.4	1.47	14700	0.84	7.4	500	91	8	3	0.01	87	0.01	7.8	32	0.01
KL20-04	419.4	421.5	0.86	8600	0.2	4.8	1410	510	6	21	2	102	0.01	10.8	32	0.01
KL20-04	421.5	424.5	0.65	6500	0.53	3.2	8000	34	14	272	10	177	1	41.2	96	0.01
KL20-04	424.5	427.5	2.44	24400	1.32	8.3	14500	15	8	1300	12	142	0.6	60.0	76	0.01
KL20-04	427.5	430.3	2.49	24900	1.91	9.9	4750	17	5	920	384	190	0.01	82.0	82	0.01
KL20-04	430.3	432.6	1.01	10100	1.16	3	389	25	27	51	141	33	0.01	12.4	74	0.01
KL20-04	432.6	434.5	6.08	60800	4.42	17.3	1250	20	22	620	5	460	0.01	62.5	87	0.01
KL20-04	434.5	436.7	0.65	6500	0.6	1.5	62	8	27	78	3	8	0.2	8.6	76	0.01
KL20-04	436.7	439.1	0.348	3480	0.4	0.01	53	11	18	74	0.01	4	0.01	6.2	86	0.01
KL20-04	439.1	442.1	0.25	2500	0.29	0.01	53	7	4	67	0.01	6	0.01	4.5	164	0.01
KL20-04	442.1	444.7	0.18	1800	0.1	0.01	23	8	2	193	0.01	6	0.01	5.9	133	0.01
KL20-04	444.7	446.9	0.157	1570	0.16	0.01	30	8	6	510	0.01	7	0.01	7.0	141	0.01
KL20-04	446.9	449.3	0.139	1390	0.04	0.01	30	8	15	390	0.01	4	0.01	6.3	182	0.01
KL20-04	449.3	451.5	0.176	1760	0.13	0.01	95	15	11	640	0.01	5	0.01	3.2	97	0.01
KL20-04	451.5	453.9	0.141	1410	0.37	0.01	34	10	5	250	0.01	5	0.01	3.9	160	0.01
KL20-04	453.9	455.6	0.26	2600	0.21	0.01	570	70	40	44	0.01	4	0.01	3.9	78	0.01
KL20-04	455.6	458.5	0.106	1060	0.23	0.01	214	18	36	630	0.01	3	0.01	3.0	61	0.01
KL20-04	458.5	460.2	0.63	6300	1.15	0.9	293	32	87	460	3	7	0.01	9.8	45	0.01
KL20-04	460.2	463.2	1.34	13400	2.52	3.3	3300	630	36	2550	4	32	0.2	18.0	30	0.01
KL20-04	463.2	466.2	1.09	10900	1.08	5.2	1010	12	68	140	0.01	21	0.01	14.1	23	0.01
KL20-04	466.2	468.1	1.67	16700	1.52	9	1350	30	97	127	0.01	52	0.7	13.0	25	0.01
KL20-04	468.1	471.1	0.081	810	0.24	0.01	153	35	21	39	5	6	1	1.4	53	0.01
KL20-04	471.1	473.2	0.0182	182	0.15	0.01	57	34	16	34	5	5	0.3	0.0	47	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL20-04	473.2	475.5	0.034	340	0.19	0.01	112	57	30	370	30	8	1.3	1.5	52	0.01
KL20-04	475.5	477.5	1.48	14800	1.5	12.6	5500	362	44	2230	14	73	1.4	16.5	61	0.01
KL20-04	477.5	479.5	0.0107	107	0.01	0.01	53	17	2	16	0.01	3	0.01	0.5	11	0.01
KL20-04	479.5	481.5	0.0184	184	0.01	0.01	90	36	2	30	0.01	2	0.3	0.6	10	0.01
KL20-04	481.5	484.5	0.0026	26	0.01	0.01	16	8	2	3	0.01	2	0.3	0.5	12	0.01
KL20-04	484.5	489.4	0.0059	59	0.01	0.01	17	14	3	3	0.01	3	0.01	0.8	20	0.01
KL20-04	489.4	492.5	0.0024	24	0.01	0.01	14	8	4	3	0.01	2	0.2	0.0	12	0.01
KL20-04	492.5	495.6	0.0085	85	0.01	0.01	34	14	6	10	0.01	2	1.1	2.1	22	0.01
KL20-04	495.6	498.7	0.0051	51	0.01	0.01	29	9	3	4	0.01	0.01	0.4	0.5	15	0.01
KL20-04	498.7	501.7	0.0072	72	0.01	0.01	14	11	4	10	0.01	0.01	0.01	1.2	20	0.01
KL20-05	0	2.7	0.0058	58	0.08	3	510	237	19	11	0.01	0.01	1.7	4.9	21	0.01
KL20-05	2.7	6	0.0042	42	0.06	2	530	570	17	7	0.01	0.01	2.4	4.8	25	0.01
KL20-05	6	9	0.0031	31	0.02	0.6	66	73	3	6	0.01	0.01	0.9	4.0	22	0.01
KL20-05	9	12	0.0025	25	0.02	0.9	178	184	2	6	0.01	0.01	0.8	3.8	25	0.01
KL20-05	12	15	0.002	20	0.01	0.6	70	102	2	6	0.01	0.01	0.7	1.7	20	0.01
KL20-05	15	18	0.0026	26	0.01	1.1	97	107	3	8	0.01	0.01	0.9	2.6	26	0.01
KL20-05	18	21	0.0023	23	0.01	1.1	254	440	5	3	0.01	0.01	0.7	3.7	26	0.01
KL20-05	21	24	0.0099	99	0.01	0.5	67	75	0.01	3	0.01	0.01	1	1.8	25	0.01
KL20-05	24	26.6	0.0045	45	0.02	1.4	760	430	12	2	0.01	0.01	1.3	3.9	26	0.01
KL20-05	26.6	29.6	0.0224	224	0.02	1	372	334	2	5	0.01	0.01	1.6	2.8	27	0.01
KL20-05	29.6	31.6	0.002	20	0.01	0.9	226	134	3	8	0.01	0.01	0.7	2.4	30	0.01
KL20-05	31.6	34.5	0.0036	36	0.02	1.4	243	311	4	10	0.01	0.01	1.2	3.9	26	0.01
KL20-05	34.5	37.5	0.006	60	0.07	7.8	780	2275	19	21	4	0.01	5.5	13.5	27	0.01
KL20-05	37.5	40.4	0.0032	32	0.03	4.2	490	510	14	14	0.01	0.01	1.7	5.3	15	0.01
KL20-05	40.4	43.3	0.0018	18	0.02	3.1	393	209	15	20	0.01	0.01	1.3	3.6	14	0.01
KL20-05	43.3	46.3	0.0022	22	0.02	4.3	1070	750	9	14	0.01	0.01	2.8	5.6	13	0.01
KL20-05	46.3	48	0.0028	28	0.05	7.1	970	560	14	10	0.01	0.01	3.7	5.1	17	0.01
KL20-05	48	51	0.0015	15	0.02	3.2	232	147	5	11	0.01	0.01	0.8	2.4	17	0.01
KL20-05	51	54	0.0016	16	0.02	4.6	780	329	11	8	0.01	0.01	1.4	5.1	17	0.01
KL20-05	54	56.6	0.0017	17	0.02	3.5	359	440	6	6	0.01	0.01	1.2	5.3	21	0.01
KL20-05	56.6	60	0.0018	18	0.03	3.5	252	222	6	7	0.01	0.01	0.6	3.8	14	0.01
KL20-05	60	63	0.0073	73	0.04	7.3	1550	2925	19	83	0.01	0.01	4.9	17.5	16	0.01
KL20-05	63	66	0.0041	41	0.03	5.1	272	259	16	11	0.01	0.01	1.6	3.0	17	0.01
KL20-05	66	68.8	0.0066	66	0.02	4.6	810	530	11	9	0.01	0.01	1.9	4.1	18	0.01
KL20-05	68.8	71.8	0.0054	54	0.04	7.8	4400	2625	11	8	0.01	0.01	4.7	11.0	12	0.24
KL20-05	71.8	74.9	0.0158	158	0.1	28.5	19900	19100	35	11	0.01	0.01	18	29.9	11	0.79
KL20-05	74.9	78	0.0025	25	0.04	6.9	8100	5600	3	5	0.01	0.01	4	11.5	17	0.18
KL20-05	78	81	0.002	20	0.02	2.2	1470	910	5	4	0.01	0.01	1.3	4.2	15	0.01
KL20-05	81	82.5	0.0115	115	0.03	1.7	2280	3100	26	7	0.01	0.01	1	5.8	16	0.01
KL20-05	82.5	85.5	0.0056	56	0.02	1.6	1890	2100	9	8	0.01	0.01	2.7	8.1	16	0.01
KL20-05	85.5	88.5	0.0045	45	0.01	2.4	1150	1250	7	8	4	0.01	0.7	6.0	17	0.01
KL20-05	88.5	91.5	0.0038	38	0.01	0.8	256	368	8	6	1	0.01	0.01	3.1	14	0.01
KL20-05	91.5	94.5	0.0033	33	0.03	1.6	630	860	9	10	0.01	0.01	0.8	6.8	17	0.01
KL20-05	94.5	97.5	0.0076	76	0.03	0.8	295	170	10	7	0.01	0.01	0.5	4.9	19	0.01
KL20-05	97.5	100.5	0.0054	54	0.08	1.1	440	205	16	6	0.01	0.01	0.01	2.8	22	0.01
KL20-05	100.5	102.3	0.0023	23	0.02	1.7	690	750	4	10	0.01	0.01	0.8	5.3	17	0.01
KL20-05	102.3	105.5	0.0193	193	0.08	0.9	348	63	13	7	0.01	0.01	0.01	2.5	18	0.01
KL20-05	105.5	108	0.0091	910	0.18	1	1630	54	20	8	0.01	3	0.7	3.8	26	0.01
KL20-05	108	111	0.106	1060	0.46	2.1	7200	353	16	15	3	16	0.8	12.8	32	0.01
KL20-05	111	113.8	0.23	2300	0.57	4.1	7300	386	28	5	8	12	0.9	16.4	21	0.01
KL20-05	113.8	116.9	0.0254	254	0.07	0.9	1720	79	7	7	1	0.01	0.01	5.8	26	0.01
KL20-05	116.9	118.5	0.0359	359	0.16	1.4	3650	28	12	4	2	0.01	0.01	12.0	20	0.01
KL20-05	118.5	121.5	0.0295	295	0.12	1.4	1560	430	12	9	5	0.01	0.3	11.9	21	0.01
KL20-05	121.5	124.5	0.045	450	0.26	1.6	2260	160	14	8	10	0.01	0.5	18.3	23	0.01
KL20-05	124.5	127.5	0.062	620	0.38	1.8	3000	291	13	8	9	3	0.2	28.0	24	0.01
KL20-05	127.5	130.5	0.41	4100	0.57	4.3	4450	440	52	7	30	3	1.8	45.1	25	0.01
KL20-05	130.5	134.8	0.51	5100	0.99	3.8	21400	234	55	15	23	21	2	52.0	27	0.01
KL20-05	134.8	138	0.6	6000	1.15	9.7	19200	114	11	95	267	19	1	104.0	69	0.01
KL20-05	138	142.7	0.337	3370	0.85	5	1390	140	93	208	230	19	2.3	38.8	170	0.01
KL20-05	142.7	147	0.24	2400	0.96	1.9	920	55	84	321	84	6	5.3	40.0	172	0.01
KL20-05	147	150	1.23	12300	2.13	3.2	281	18	7	980	4	14	0.01	18.8	99	0.01
KL20-05	150	153	0.98	9800	2.9	3.4	580	19	21	410	34	11	0.5	18.0	67	0.01
KL20-05	153	156	0.43	4300	1.02	1.9	256	47	30	560	4	7	0.4	11.5	73	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL20-05	156	159	0.42	4200	1.58	2.1	500	73	77	180	20	12	2.3	14.5	87	0.01
KL20-05	159	162	1.04	10400	1.46	3.2	680	96	48	350	6	11	1.9	13.0	85	0.01
KL20-05	162	165	0.4	4000	4.42	2.6	8000	191	60	400	84	9	1.1	30.4	43	0.01
KL20-05	165	168	1.41	14100	1.18	6.9	2400	810	24	1770	12	26	0.5	40.0	47	0.01
KL20-05	168	171	1.04	10400	1.32	4.2	460	45	16	510	1	23	0.3	14.0	91	0.01
KL20-05	171	174	0.59	5900	1.12	3.5	590	25	18	110	4	16	0.3	22.5	60	0.01
KL20-05	174	177	0.294	2940	0.7	2.5	224	14	37	1250	2	13	0.4	21.0	89	0.01
KL20-05	177	180.1	0.369	3690	1.57	2.5	350	19	16	2200	37	16	0.4	41.3	95	0.01
KL20-05	180.1	181.7	2.65	26500	3.98	6.4	375	16	9	770	112	6	0.3	47.0	60	0.01
KL20-05	181.7	184.5	3.96	39600	8.58	17.7	1300	11	6	260	82	49	0.5	80.5	30	0.01
KL20-05	184.5	187.5	0.98	9800	2.36	4.9	235	20	13	160	30	11	0.3	85.7	43	0.01
KL20-05	187.5	190.5	1.88	18800	3.9	5.6	185	10	24	60	16	24	0.4	68.0	45	0.01
KL20-05	190.5	193.5	0.048	480	0.01	0.6	116	30	6	7	0.01	6	0.2	0.0	63	0.01
KL20-05	193.5	195.8	1.4	14000	0.86	4.8	172	39	37	270	12	90	5	32.2	118	0.01
KL20-05	195.8	198.1	2.51	25100	0.68	5.8	194	19	2	260	0.01	73	0.3	40.5	90	0.5
KL20-05	198.1	201	0.81	8100	0.3	1.6	89	7	1	300	2	33	0.01	9.0	23	0.01
KL20-05	201	204	0.044	440	0.01	0.01	59	17	2	7	1	12	0.3	1.3	50	0.01
KL20-05	204	207	3.39	33900	1.14	7.4	121	37	4	118	3	21	0.2	31.0	67	0.01
KL20-05	207	210	1.02	10200	0.34	3.2	173	50	15	240	3	10	1	9.5	124	0.01
KL20-05	210	213	0.57	5700	0.23	1.6	234	45	28	170	3	6	0.9	6.0	120	0.01
KL20-05	213	216	3.57	35700	1.26	11.2	81	27	5	18	9	20	0.01	24.0	57	0.1
KL20-05	216	219	9.83	98300	1.43	22.7	100	28	4	27	38	14	0.01	9.0	167	0.01
KL20-05	219	220.7	5.05	50500	1.18	19.4	1500	2200	1700	25	42	13	6.8	25.0	193	0.42
KL20-05	220.7	222.9	7.88	78800	1.44	48	5750	3300	15000	6	52	47	28	62.0	52	1.65
KL20-05	222.9	226.5	2.5	25000	0.92	5.6	327	105	750	22	9	17	2.8	19.0	172	0.11
KL20-05	226.5	229.5	3.43	34300	1.15	6.5	75	27	40	107	2	16	0.01	16.0	61	0.1
KL20-05	229.5	232.5	9.45	94500	3.46	17.3	76	15	7	640	2	27	0.4	17.5	110	0.22
KL20-05	232.5	235.5	11.4	114000	4.38	19	121	22	15	20	4	56	0.01	25.0	56	0.1
KL20-05	235.5	238.5	10.5	105000	1.97	9.6	123	17	28	93	8	23	0.01	15.0	192	0.01
KL20-05	238.5	241	8.2	82000	2.27	13.6	94	18	20	22	8	17	0.2	15.0	74	0.41
KL20-05	241	243	2.63	26300	0.41	3.8	152	46	170	227	3	10	6.3	7.0	150	0.01
KL20-05	243	246	0.91	9100	0.35	1.7	51	20	36	509	1	7	1.1	11.0	52	0.01
KL20-05	246	248.5	2.74	27400	0.44	5	1030	266	300	590	2	11	26	13.5	67	0.22
KL20-05	248.5	250.5	6.22	62200	20.8	11.2	214	21	30	2830	2	90	0.01	30.0	120	0.01
KL20-05	250.5	252.4	3.26	32600	2.57	4.2	102	14	11	1700	1	53	0.01	18.0	147	0.01
KL20-05	252.4	254.5	11	110000	6.2	8.9	98	11	2	870	1	102	0.01	17.5	76	0.01
KL20-05	254.5	256.8	6.12	61200	3.57	7.4	76	11	1	890	1	100	0.01	10.5	132	0.01
KL20-05	256.8	259.5	1.57	15700	1.28	3.7	99	16	14	79	12	22	0.3	48.6	136	0.01
KL20-05	259.5	262.5	1.15	11500	0.72	5.5	183	20	44	17	37	12	0.5	47.0	61	0.01
KL20-05	262.5	265.5	2.73	27300	2.72	9.5	420	36	34	8	64	14	1.1	40.3	73	0.01
KL20-05	265.5	268.3	1.28	12800	2.2	5.9	670	158	34	162	510	20	3.1	56.3	128	0.1
KL20-05	268.3	271.5	0.39	3900	0.84	5.5	340	334	38	9	830	7	1.6	70.0	76	0.01
KL20-05	271.5	274.5	0.775	7750	3.14	6.7	5400	230	38	208	18	29	0.4	55.6	23	0.01
KL20-05	274.5	277.5	0.357	3570	2.17	4.4	32100	1030	250	6	22	24	2.5	50.6	26	0.01
KL20-05	277.5	279	0.0135	135	0.59	5	3350	4670	300	10	6	4	4.4	11.2	22	0.01
KL20-05	279	281.3	0.0072	72	0.4	0.9	620	306	230	3	2	0.01	1.3	4.0	27	0.01
KL20-05	281.3	283.5	0.0058	58	0.02	0.01	74	51	13	9	2	0.01	0.2	1.3	31	0.01
KL20-05	283.5	286.5	0.0093	93	0.08	1	790	324	31	5	3	0.01	0.4	1.4	15	0.01
KL20-05	286.5	289.5	0.004	40	0.14	0.01	180	70	17	4	0.01	0.01	0.3	1.3	17	0.01
KL20-05	289.5	292.5	0.0047	47	0.04	0.01	364	29	19	3	0.01	0.01	0.01	1.7	18	0.01
KL20-05	292.5	295.5	0.0034	34	0.09	0.01	74	36	40	2	0.01	0.01	0.3	1.8	29	0.01
KL20-05	295.5	298.3	0.0029	29	0.21	1.1	610	317	41	7	1	2	0.8	2.8	23	0.01
KL20-05	298.3	300.8	0.087	870	0.68	33.7	35200	22700	240	55	66	0.01	6.6	38.5	24	0.14
KL20-05	300.8	303.3	0.0092	92	0.18	2.5	820	1090	40	6	2	0.01	1.4	4.8	18	0.01
KL20-05	303.3	306	0.0021	21	0.19	0.01	167	187	29	3	0.01	0.01	0.3	0.0	18	0.01
KL20-05	306	309	0.0015	15	0.03	0.01	140	81	17	3	0.01	0.01	0.5	1.4	15	0.01
KL20-05	309	312	0.0017	17	0.01	0.01	50	46	18	4	1	0.01	0.4	0.0	16	0.01
KL20-05	312	315	0.0018	18	0.02	0.01	95	54	17	3	0.01	0.01	0.5	0.5	18	0.01
KL20-05	315	318	0.0013	13	0.01	0.5	82	78	13	3	0.01	0.01	0.01	0.0	19	0.01
KL20-05	318	319.5	0.0028	28	0.04	0.5	83	95	29	3	0.01	0.01	0.8	0.0	23	0.01
KL20-05	319.5	322.5	0.0029	29	0.04	1.8	368	49	22	5	0.01	2	0.6	0.0	16	0.01
KL20-05	322.5	325.5	0.0032	32	0.01	0.01	90	67	22	2	0.01	2	0.6	0.0	17	0.01
KL20-05	325.5	328.5	0.002	20	0.01	0.01	114	102	21	3	0.01	0.01	0.4	0.0	18	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL20-05	328.5	331.5	0.0076		76	0.01	0.01	149	32	18	7	5	0.01	0.01	1.3	14	0.01
KL20-05	331.5	334.5	0.0022		22	0.01	0.01	102	37	16	8	0.01	0.01	0.4	0.8	16	0.01
KL20-05	334.5	337.5	0.0021		21	0.01	0.01	73	18	16	3	0.01	2	0.01	0.6	14	0.01
KL20-05	337.5	340.5	0.0037		37	0.01	0.01	52	10	21	3	0.01	0.01	0.01	0.7	12	0.01
KL20-05	340.5	343.5	0.0023		23	0.01	0.01	31	20	19	3	0.01	0.01	0.01	0.6	0	0.01
KL20-05	343.5	346.5	0.0049		49	0.02	0.01	107	13	29	3	0.01	0.01	0.01	0.6	11	0.01
KL20-05	346.5	349.5	0.0063		63	0.02	0.01	127	23	29	4	1	0.01	0.5	0.6	8	0.01
KL20-05	349.5	352.5	0.0107		107	0.01	0.01	193	14	21	7	1	2	0.8	0.0	10	0.01
KL20-05	352.5	355.5	0.0087		87	0.02	0.01	133	16	26	6	0.01	3	0.5	1.0	13	0.01
KL20-05	355.5	358.5	0.0049		49	0.01	0.01	81	7	26	59	0.01	0.01	0.01	0.9	11	0.01
KL20-05	358.5	361.5	0.005		50	0.01	0.01	90	16	23	6	1	0.01	0.01	1.0	8	0.01
KL20-05	361.5	363	0.0076		76	0.02	0.01	118	14	25	7	1	2	0.01	1.2	8	0.01
KL20-05	363	366	0.0034		34	0.01	0.01	72	16	18	4	1	0.01	0.01	0.7	8	0.01
KL20-05	366	369	0.0036		36	0.01	0.01	80	30	19	5	2	0.01	0.01	0.8	10	0.01
KL20-05	369	372	0.0034		34	0.01	0.01	112	26	16	3	1	2	0.01	0.8	12	0.01
KL20-05	372	375	0.0048		48	0.01	0.01	78	38	13	13	2	0.01	0.4	1.0	11	0.01
KL20-05	375	378	0.0058		58	0.05	0.01	100	46	14	8	3	3	1	0.9	15	0.01
KL20-05	378	381	0.0079		79	0.02	0.01	119	17	21	0.01	0.01	2	0.2	0.0	12	0.01
KL20-05	381	384	0.0055		55	0.02	0.01	81	30	17	3	0.01	2	0.3	2.1	14	0.11
KL20-05	384	387	0.003		30	0.01	0.01	30	13	15	0.01	0.01	3	0.01	0.0	17	0.01
KL20-05	387	390	0.0036		36	0.01	0.01	36	12	16	0.01	0.01	0.01	0.2	0.0	21	0.01
KL20-05	390	393	0.0026		26	0.02	0.01	28	10	12	0.01	0.01	3	1	0.0	16	0.01
KL20-05	393	396	0.0054		54	0.02	0.01	85	10	8	5	0.01	2	0.2	0.0	13	0.01
KL20-05	396	399	0.0067		67	0.01	0.01	54	12	13	9	0.01	2	0.6	0.0	14	0.01
KL20-05	399	402	0.0065		65	0.02	0.01	61	45	17	13	0.01	0.01	1.6	1.1	11	0.01
KL20-05	402	405	0.017		170	0.05	0.5	530	30	25	7	4	2	0.6	1.0	12	0.01
KL20-05	405	408	0.04		400	0.02	0.9	750	38	13	7	7	2	1.3	2.0	16	0.01
KL20-05	408	411	0.0385		385	0.02	0.9	510	41	12	4	5	0.01	0.4	2.5	12	0.01
KL20-05	411	414	0.0241		241	0.03	0.8	560	50	19	5	4	4	0.5	3.0	12	0.01
KL20-05	414	417	0.0067		67	0.01	0.01	59	16	14	3	1	0.01	0.01	1.2	13	0.01
KL20-05	417	420	0.0124		124	0.02	0.5	271	74	20	5	2	2	0.3	1.7	11	0.01
KL20-05	420	423	0.0127		127	0.01	0.01	94	51	24	5	2	2	0.5	0.9	13	0.01
KL20-05	423	426	0.008		80	0.05	0.01	39	31	29	3	0.01	2	0.6	1.2	22	0.01
KL20-05	426	429	0.0035		35	0.03	0.01	18	15	30	3	0.01	2	0.4	2.1	17	0.01
KL20-05	429	432	0.0032		32	0.01	0.01	14	11	37	0.01	0.01	0.01	0.4	3.0	11	0.01
KL20-05	432	433.5	0.043		430	0.05	0.5	58	24	38	22	0.01	3	0.3	3.8	45	0.01
KL20-06	0	3	0.0064		64	0.06	3.6	359	194	9	5	0.01	0.01	2.2	3.8	25	0.01
KL20-06	3	6	0.0026		26	0.06	1.4	229	130	8	2	0.01	0.01	0.6	1.7	24	0.01
KL20-06	6	8.5	0.0011		11	0.02	0.6	182	120	2	3	0.01	0.01	0.01	0.9	28	0.01
KL20-06	8.5	11.8	0.0012		12	0.02	0.01	66	99	1	4	0.01	0.01	0.4	1.4	26	0.01
KL20-06	11.8	14.1	0.0042		42	0.02	0.01	69	60	2	3	0.01	0.01	0.5	2.3	28	0.01
KL20-06	14.1	16.3	0.0021		21	0.03	1.1	360	228	2	3	0.01	0.01	0.7	4.7	26	0.01
KL20-06	16.3	19.4	0.001		10	0.02	0.01	140	88	2	4	0.01	0.01	0.4	2.0	28	0.01
KL20-06	19.4	22.5	0.001		10	0.02	0.01	91	90	1	3	0.01	0.01	0.6	1.4	28	0.01
KL20-06	22.5	25.5	0.0026		26	0.01	1.1	148	1010	3	3	0.01	2	1.4	2.4	27	0.01
KL20-06	25.5	28.5	0.0012		12	0.02	0.01	113	113	1	2	0.01	0.01	0.2	1.8	35	0.01
KL20-06	28.5	31.5	0.0008		8	0.01	0.01	34	69	1	8	0.01	0.01	0.2	1.1	33	0.01
KL20-06	31.5	34.5	0.0012		12	0.01	1	1570	930	1	13	0.01	0.01	1.2	5.8	36	0.01
KL20-06	34.5	37.5	0.0009		9	0.01	0.01	540	285	2	2	0.01	2	0.2	1.1	31	0.01
KL20-06	37.5	40.5	0.0007		7	0.01	0.01	256	127	2	2	0.01	2	0.9	0.7	36	0.01
KL20-06	40.5	45	0.0013		13	0.04	0.7	222	218	5	8	0.01	0.01	1	4.1	36	0.01
KL20-06	45	48	0.0042		42	0.02	0.01	166	148	2	13	0.01	2	0.4	1.0	42	0.01
KL20-06	48	51	0.0013		13	0.03	0.01	322	79	3	14	0.01	2	0.4	0.9	41	0.01
KL20-06	51	54.7	0.0019		19	0.02	0.8	610	247	3	7	0.01	0.01	0.5	1.0	31	0.01
KL20-06	54.7	57.8	0.0024		24	0.01	1.3	303	282	5	10	0.01	0.01	0.7	1.7	16	0.01
KL20-06	57.8	61	0.0041		41	0.04	4.2	3700	2800	9	9	0.01	2	2.8	8.5	18	0.01
KL20-06	61	64.2	0.0039		39	0.01	1.5	326	286	9	13	0.01	2	1.8	2.2	18	0.01
KL20-06	64.2	67.4	0.0028		28	0.01	1.4	358	640	6	12	0.01	2	0.7	4.7	17	0.01
KL20-06	67.4	70.5	0.0021		21	0.01	1.2	420	428	5	17	0.01	0.01	0.3	3.0	16	0.01
KL20-06	70.5	73.5	0.0016		16	0.01	0.8	355	311	4	14	0.01	0.01	0.3	1.8	17	0.01
KL20-06	73.5	76.5	0.0015		15	0.01	0.01	140	240	5	12	0.01	0.01	0.01	2.5	18	0.01
KL20-06	76.5	79.5	0.0013		13	0.01	0.5	113	227	4	7	0.01	0.01	0.01	1.6	20	0.01
KL20-06	79.5	82.5	0.0014		14	0.01	1.1	115	128	7	6	0.01	0.01	0.3	1.2	15	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL20-06	82.5	85.5	0.0013		13	0.01	1.2	164	141	4	4	0.01	0.01	0.5	1.3	15	0.01
KL20-06	85.5	88.5	0.0012		12	0.01	2	369	670	3	3	0.01	0.01	0.7	4.6	11	0.01
KL20-06	88.5	91.5	0.0016		16	0.01	1.1	231	340	4	15	0.01	0.01	0.2	3.2	14	0.01
KL20-06	91.5	94.5	0.0016		16	0.01	0.8	148	199	4	4	0.01	0.01	0.3	2.0	18	0.01
KL20-06	94.5	96.7	0.0009		9	0.02	1.2	170	224	11	5	0.01	0.01	0.8	1.8	15	0.01
KL20-06	96.7	99	0.0021		21	0.02	3.6	163	170	9	5	0.01	0.01	1.2	3.0	21	0.01
KL20-06	99	102	0.0244		244	0.13	103	30800	15400	36	4	0.01	0.01	81	28.5	20	0.01
KL20-06	102	105	0.0048		48	0.03	3.1	1850	1520	10	24	0.01	0.01	2.1	4.3	13	0.01
KL20-06	105	108	0.0093		93	0.02	1.3	363	750	5	6	0.01	2	1.2	2.0	26	0.01
KL20-06	108	111	0.0091		91	0.02	3	2000	2030	6	5	0.01	0.01	2.5	3.0	24	0.01
KL20-06	111	114	0.0028		28	0.02	1.3	690	1180	11	9	0.01	2	1.9	5.6	20	0.01
KL20-06	114	116.7	0.0102		102	0.05	3.2	3500	6000	9	33	3	2	1.1	58.8	22	0.01
KL20-06	116.7	119.8	0.0063		63	0.02	6	4400	4100	21	15	0.01	2	5.6	10.1	22	0.01
KL20-06	119.8	122.9	0.0062		62	0.02	2.4	830	1440	16	22	3	0.01	1.1	7.7	16	0.01
KL20-06	122.9	126	0.0132		132	0.08	3.7	2500	2600	9	50	26	2	0.7	17.4	16	0.01
KL20-06	126	129	0.0101		101	0.07	4.2	1060	1590	8	43	41	0.01	0.7	15.8	14	0.01
KL20-06	129	132	0.0139		139	0.13	3	1190	2010	15	17	14	2	0.6	36.5	15	0.01
KL20-06	132	135	0.024		240	0.14	6.4	3400	1650	37	48	4	3	1.1	14.5	19	0.01
KL20-06	135	138	0.053		530	0.15	4.7	4300	1560	12	7	2	2	1.6	19.3	15	0.1
KL20-06	138	141	0.0032		32	0.13	2.3	480	550	14	3	1	2	1.1	13.7	13	0.01
KL20-06	141	144	0.063		630	0.25	6.8	1910	1650	150	81	17	4	6.3	14.2	32	0.1
KL20-06	144	147	0.093		930	0.28	4.9	2700	1840	27	63	25	4	2.1	19.0	31	0.01
KL20-06	147	150	0.0374		374	0.17	6.8	4800	19200	25	306	21	2	2.2	48.8	22	0.01
KL20-06	150	153	0.0328		328	0.08	2	1880	1290	20	53	16	0.01	0.6	7.4	14	0.01
KL20-06	153	156	0.087		870	0.18	5.7	6500	2760	22	132	62	5	0.9	16.5	24	0.01
KL20-06	156	159	0.0302		302	0.12	5	3000	2300	40	76	34	2	2.6	6.6	22	0.12
KL20-06	159	162.5	0.045		450	0.1	1.6	1290	620	11	18	9	4	0.4	4.0	15	0.01
KL20-06	162.5	165.5	0.0288		288	0.06	1	590	570	16	8	7	3	0.3	3.5	16	0.01
KL20-06	165.5	168.5	0.051		510	0.06	0.8	870	204	29	9	6	2	1.4	3.8	14	0.01
KL20-06	168.5	170.6	0.098		980	0.17	0.9	2900	202	31	17	11	5	0.8	8.0	14	0.1
KL20-06	170.6	174	0.168		1680	0.35	1.8	3100	162	35	24	14	7	1.1	12.7	22	0.01
KL20-06	174	177	0.142		1420	0.27	2.5	2900	1040	20	7	18	4	0.6	31.0	16	0.01
KL20-06	177	179.2	0.4		4000	0.48	2.8	1890	48	61	49	14	13	3.2	15.7	55	0.11
KL20-06	179.2	181.5	0.31		3100	0.45	2.7	7000	46	31	35	20	14	0.5	49.0	33	0.01
KL20-06	181.5	184.5	0.79		7900	1.68	8.8	3400	294	890	830	38	16	56	49.0	227	0.23
KL20-06	184.5	187.5	0.36		3600	0.75	4.4	620	110	410	790	14	8	19.3	22.6	303	0.1
KL20-06	187.5	190.5	0.33		3300	0.5	4.5	820	394	280	382	8	11	5.6	7.9	256	0.01
KL20-06	190.5	192.3	0.63		6300	0.52	2.1	192	76	100	1380	5	10	3.1	11.6	270	0.01
KL20-06	192.3	194.7	1.12		11200	1.38	2.4	470	15	9	190	2	31	1.3	20.2	45	0.01
KL20-06	194.7	196.5	0.133		1330	0.66	1	388	38	33	140	298	10	1.4	14.8	43	0.01
KL20-06	196.5	199.5	0.34		3400	0.22	0.9	274	22	28	530	2	10	1.3	42.3	38	0.01
KL20-06	199.5	202.5	0.82		8200	0.5	1.3	610	42	25	890	3	23	1.9	12.7	49	0.01
KL20-06	202.5	205.4	0.48		4800	1.33	10.5	5850	2500	370	2260	37	17	6.1	43.5	127	0.01
KL20-06	205.4	208.5	1.89		18900	1.16	4.9	980	229	51	2100	9	40	3.3	8.1	58	0.1
KL20-06	208.5	211.5	0.51		5100	0.52	1.5	430	78	57	580	6	22	2.9	13.1	52	0.1
KL20-06	211.5	214.5	0.93		9300	0.82	4.1	3000	1320	210	2200	11	25	5.8	28.0	98	0.01
KL20-06	214.5	217.5	0.28		2800	0.64	2.5	480	162	260	1360	4	14	3.3	11.6	95	0.1
KL20-06	217.5	220.5	1.13		11300	1.23	20	10700	9900	1170	1070	35	20	14	22.6	211	1.04
KL20-06	220.5	223.5	0.48		4800	0.43	1.4	1580	88	39	5000	7	15	1.5	11.8	109	0.01
KL20-06	223.5	226.5	1		10000	0.55	2.1	3800	50	36	4600	16	14	0.7	20.4	68	0.01
KL20-06	226.5	228.9	0.59		5900	0.53	2.2	7100	44	50	4300	10	12	0.4	21.0	57	0.01
KL20-06	228.9	231.9	1.5		15000	2.07	10.8	29700	77	110	2300	12	31	1.8	32.7	78	0.01
KL20-06	231.9	234.9	1.63		16300	4.55	6.6	63000	39	34	293	80	43	0.5	83.8	53	0.01
KL20-06	234.9	237.9	0.71		7100	3.37	3.5	22000	142	34	226	3	32	1.5	30.8	135	0.01
KL20-06	237.9	240.9	0.8		8000	3.91	4.8	1960	46	31	128	3	36	1.5	8.0	130	0.01
KL20-06	240.9	243.9	1		10000	1.26	1.4	920	20	11	460	1	36	0.7	21.4	18	0.01
KL20-06	243.9	246.9	0.92		9200	0.84	3.1	2400	1330	100	279	1	32	6.5	22.0	32	0.01
KL20-06	246.9	249.9	0.68		6800	1.08	1.4	333	23	21	388	1	31	0.8	38.8	76	0.01
KL20-06	249.9	252.9	1.34		13400	1.85	2.7	2000	30	7	232	1	43	0.8	67.5	47	0.01
KL20-06	252.9	255.9	1.66		16600	1.31	1	900	13	2	430	2	68	0.01	21.5	19	0.01
KL20-06	255.9	258.9	0.77		7700	1.54	1.3	8000	33	10	42	2	60	0.01	22.6	21	0.01
KL20-06	258.9	261.9	1.2		12000	2.1	1.4	1490	47	24	36	2	54	0.01	19.4	27	0.2
KL20-06	261.9	264.9	0.71		7100	5.42	12.7	23100	3300	610	17	19	61	20.3	42.5	39	0.68

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL20-07	375	378														
KL20-07	378	381														
KL20-07	381	384														
KL20-07	384	387														
KL20-07	387	389.4	1.51	15100	1.65	1.9	95	9	1	7	0.01	21	0.01	5.0	55	0.01
KL20-08	270	273	1.39	13900	1.09	3.7	191	13	7	100	1	38	0.01	7.8	28	0.01
KL20-08	273	276	1.79	17900	1.44	4.7	150	12	2	60	3	17	0.01	16.2	36	0.01
KL20-08	276	279	1.14	11400	0.76	2.9	97	9	1	40	1	16	0.01	8.0	30	0.01
KL20-08	279	282	2.75	27500	7.64	6.7	124	11	0.01	70	4	47	0.01	13.7	24	0.01
KL20-08	282	285	1.14	11400	0.8	2.5	101	17	4	985	1	15	0.01	4.2	67	0.01
KL20-08	285	288	1.4	14000	1.14	2.5	91	13	2	633	0.01	27	0.01	5.0	72	0.01
KL20-08	288	291	1.21	12100	0.69	3	110	13	3	1100	0.01	27	0.01	7.5	84	0.01
KL20-08	291	294	1.5	15000	1.2	3.9	266	53	3	223	0.01	35	0.01	9.0	83	0.01
KL20-08	294	297	0.82	8200	0.6	3	97	51	2	106	0.01	29	0.01	6.8	87	0.01
KL20-08	297	300	0.7	7000	0.33	3.9	3600	1710	12	106	3	8	1.3	4.6	77	0.01
KL20-08	300	303.2	0.64	6400	1.4	1.2	69	16	1	32	1	8	0.01	5.5	83	0.01
KL20-08	303.2	306	0.55	5500	0.47	1	65	12	2	193	0.01	11	0.01	3.8	89	0.01
KL20-08	306	309	0.68	6800	0.49	1.8	53	10	3	107	0.01	16	0.01	4.3	88	0.01
KL20-08	309	312	0.69	6900	0.18	2.3	316	91	12	191	0.01	15	1	5.2	90	0.01
KL20-08	312	315	0.85	8500	0.62	2	295	95	3	365	1	14	0.7	6.0	69	0.01
KL20-08	315	318	0.97	9700	0.83	2.4	75	11	3	210	0.01	19	0.6	4.8	81	0.01
KL20-08	318	321	0.79	7900	0.73	1.1	63	16	1	90	0.01	15	0.8	5.6	73	0.01
KL20-08	321	324	0.91	9100	0.91	1.6	120	22	4	39	2	16	0.01	5.6	72	0.01
KL20-08	324	327	0.68	6800	0.68	1.1	45	8	1	50	1	14	0.2	5.6	64	0.01
KL20-08	327	330	0.81	8100	0.5	1.4	70	10	3	69	0.01	17	0.01	5.0	61	0.01
KL20-08	330	333	0.85	8500	0.44	2.3	84	11	2	75	0.01	14	0.01	4.6	84	0.01
KL20-08	333	336	0.71	7100	1.3	1.1	86	10	2	121	0.01	17	0.01	4.4	98	0.01
KL20-08	336	339	0.82	8200	0.6	2	67	7	5	243	0.01	19	0.3	7.2	74	0.01
KL20-08	339	342	0.97	9700	0.64	1.8	81	6	1	298	0.01	12	0.01	6.4	61	0.01
KL20-08	342	345	0.94	9400	0.53	2.1	68	8	2	166	0.01	15	0.01	5.8	73	0.01
KL20-08	345	348	0.71	7100	0.41	1.5	61	9	1	363	0.01	21	0.01	5.4	60	0.01
KL20-08	348	351	0.72	7200	0.48	1.4	54	8	2	148	0.01	19	0.01	6.7	68	0.01
KL20-08	351	354	0.486	4860	0.4	1	65	11	0.01	165	0.01	13	0.01	5.1	57	0.01
KL20-08	354	357	0.79	7900	0.44	1.6	83	12	4	196	0.01	14	0.2	5.6	68	0.01
KL20-08	357	360	0.96	9600	0.65	2.5	84	12	3	19	0.01	15	0.01	5.2	67	0.01
KL20-08	360	363	1.05	10500	0.88	3.1	1410	27	0.01	23	0.01	17	0.2	5.4	73	0.01
KL20-08	363	366	0.85	8500	0.6	3.6	223	48	18	20	1	12	2.9	4.7	68	0.01
KL20-08	366	369	0.79	7900	0.63	1.4	75	10	0.01	12	0.01	14	0.01	9.5	64	0.01
KL20-08	369	372	1.2	12000	0.91	2.3	132	18	6	13	1	13	0.3	6.0	62	0.01
KL20-08	372	375	0.68	6800	0.49	1.9	64	12	1	143	0.01	17	0.2	3.8	70	0.01
KL20-08	375	378	1.04	10400	0.85	2.6	79	12	67	67	0.01	12	0.8	4.2	68	0.01
KL20-08	378	381	1.02	10200	0.8	1.4	84	15	64	202	0.01	14	1	3.3	70	0.01
KL20-08	381	385	0.97	9700	0.88	3.2	166	20	68	12	0.01	21	2.7	6.4	51	0.01
KL20-08	385	389	0.9	9000	0.73	2.6	73	10	5	4	0.01	13	0.01	4.6	59	0.01
KL20-08	389	391.9	1.71	17100	1.25	3.2	118	12	5	4	0.01	22	0.01	5.0	53	0.01
KL20-08	391.9	394.8	2	20000	3.24	7.1	404	29	1150	17	1	17	50	11.3	59	0.18
KL20-08	394.8	398.2	0.94	9400	0.56	3.4	108	24	85	22	2	6	19.9	4.2	45	0.01
KL20-08	398.2	401.7	0.381	3810	0.48	0.9	41	10	7	13	0.01	6	0.01	3.3	58	0.01
KL20-08	401.7	405	0.473	4730	0.27	1.2	46	29	4	14	0.01	5	0.01	3.4	38	0.01
KL20-08	405	408	0.26	2600	0.16	1	38	12	2	18	0.01	8	0.2	2.9	50	0.01
KL20-08	408	411.3	0.41	4100	0.36	0.9	45	16	2	8	0.01	7	0.3	2.8	42	0.01
KL20-08	411.3	414.2	0.56	5600	0.57	1.3	55	17	25	15	0.01	5	1.3	2.5	40	0.01
KL20-08	414.2	417	0.38	3800	0.4	1	54	11	3	13	0.01	12	0.2	4.1	60	0.01
KL20-08	417	420	0.443	4430	0.29	1.3	146	32	41	26	1	9	1.7	3.6	87	0.01
KL20-08	420	423	0.55	5500	0.29	1.4	42	12	63	32	0.01	7	0.8	2.7	67	0.01
KL20-08	423	426	0.93	9300	1.01	2.4	42	7	2	28	2	13	0.01	5.1	87	0.01
KL20-08	426	429	0.45	4500	0.35	1.2	30	6	19	19	0.01	6	0.01	2.3	42	0.01
KL20-08	429	432	0.37	3700	0.21	1.4	99	23	3	21	0.01	6	0.3	2.1	57	0.01
KL20-08	432	435	0.406	4060	0.25	1.1	76	28	8	14	0.01	8	0.4	2.7	58	0.01
KL20-08	435	438	0.87	8700	0.68	1.9	79	22	160	15	1	6	2.3	4.8	44	0.01
KL20-08	438	441	0.69	6900	0.51	1.1	40	15	12	31	0.01	6	0.2	5.0	85	0.01
KL20-08	441	444	0.525	5250	0.44	0.9	26	12	1	15	0.01	5	0.01	1.8	84	0.01
KL20-08	444	446.8	0.54	5400	0.42	1.2	24	10	2	19	0.01	6	0.4	3.5	100	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL20-08	446.8	449.8	0.515	5150	0.43	1.2	45	7	2	30	0.01	5	0.01	4.0	86	0.01
KL20-08	449.8	452.9	0.54	5400	0.17	1	60	30	3	18	0.01	5	0.01	3.0	76	0.01
KL20-08	452.9	456	0.645	6450	0.67	1.4	40	22	1	25	1	4	0.01	3.5	74	0.01
KL20-08	456	459	0.44	4400	0.41	0.9	39	17	3	11	0.01	3	0.01	3.0	298	0.01
KL20-08	459	462	0.3	3000	0.3	0.01	40	15	1	22	0.01	0.01	0.01	1.8	43	0.01
KL20-08	462	465	0.665	6650	0.58	0.7	33	17	3	51	1	4	0.2	6.5	89	0.01
KL20-08	465	468.3	0.81	8100	0.88	1.2	43	15	2	15	1	7	0.01	5.8	229	0.01
KL20-09	0	3.2	0.0097	97	0.02	1.2	266	151	4	12	0.01	0.01	0.5	3.3	28	0.01
KL20-09	3.2	6.4	0.0023	23	0.05	3.2	81	46	7	7	0.01	0.01	1	3.4	33	0.01
KL20-09	6.4	10	0.002	20	0.12	4	271	228	15	6	0.01	0.01	1.2	7.1	28	0.01
KL20-09	10	13	0.002	20	0.09	2.2	45	66	9	4	0.01	0.01	1	5.6	16	0.01
KL20-09	13	16	0.0043	43	1.13	5.8	120	107	200	9	0.01	3	3.2	3.6	22	0.01
KL20-09	16	19	0.0026	26	0.88	2.8	60	43	44	8	0.01	0.01	2.2	2.6	21	0.01
KL20-09	19	22	0.0021	21	0.15	3.9	62	25	14	7	0.01	2	1	3.2	20	0.01
KL20-09	22	25	0.006	60	0.07	1.8	91	71	7	3	0.01	0.01	0.2	2.5	23	0.01
KL20-09	25	28	0.0012	12	0.11	1.7	87	66	2	2	0.01	0.01	0.4	1.2	24	0.01
KL20-09	28	31	0.0024	24	0.04	11.3	490	660	4	6	0.01	2	1.4	2.4	26	0.01
KL20-09	31	34	0.0025	25	0.01	2.2	278	244	4	4	0.01	0.01	0.8	2.3	34	0.01
KL20-09	34	37	0.0024	24	0.01	0.01	130	110	1	5	0.01	0.01	0.5	0.8	25	0.01
KL20-09	37	40	0.0013	13	0.01	1	90	153	7	3	0.01	0.01	0.3	0.9	19	0.01
KL20-09	40	43	0.0019	19	0.01	1.5	650	330	5	3	0.01	0.01	0.8	2.1	28	0.01
KL20-09	43	46	0.001	10	0.01	0.6	154	570	3	3	0.01	0.01	0.7	1.6	26	0.01
KL20-09	46	49	0.0008	8	0.01	0.5	153	240	15	2	0.01	0.01	0.3	1.4	23	0.01
KL20-09	49	52	0.0022	22	0.01	2.8	159	278	9	3	0.01	0.01	0.5	3.3	19	0.01
KL20-09	52	55	0.0011	11	0.01	1.4	250	106	3	4	0.01	0.01	0.01	1.1	28	0.01
KL20-09	55	58	0.0015	15	0.01	4.1	273	183	7	4	0.01	0.01	0.8	2.3	25	0.01
KL20-09	58	61	0.0011	11	0.01	1.3	263	180	3	2	0.01	0.01	0.4	1.4	27	0.01
KL20-09	61	64	0.0004	4	0.01	0.6	68	278	0.01	3	0.01	0.01	0.2	1.2	31	0.01
KL20-09	64	67	0.0011	11	0.01	7.8	1010	279	8	0.01	0.01	0.01	0.6	6.7	15	0.01
KL20-09	67	70	0.0018	18	0.01	16.7	175	67	14	9	0.01	0.01	0.8	2.3	15	0.01
KL20-09	70	73	0.0013	13	0.01	3.7	119	60	11	11	0.01	0.01	0.8	0.6	16	0.01
KL20-09	73	76	0.0014	14	0.01	16.1	590	344	12	5	0.01	0.01	2.1	2.3	12	0.01
KL20-09	76	79	0.0041	41	0.01	36.5	4400	2275	25	2	0.01	0.01	4.7	8.2	15	0.01
KL20-09	79	82	0.001	10	0.01	3.2	1180	690	6	4	0.01	0.01	0.8	2.4	16	0.01
KL20-09	82	85	0.0007	7	0.01	1.1	243	206	6	3	0.01	0.01	0.01	0.8	19	0.01
KL20-09	85	88	0.0008	8	0.01	0.7	206	205	7	2	0.01	0.01	0.3	1.3	13	0.01
KL20-09	88	91	0.0015	15	0.01	1.8	650	440	11	0.01	0.01	0.01	0.2	2.3	11	0.01
KL20-09	91	94	0.0015	15	0.01	2.7	143	134	12	7	0.01	2	0.3	1.6	16	0.01
KL20-09	94	97	0.0191	191	0.1	18.4	6900	5700	27	26	1	0.01	8.5	33.7	26	0.01
KL20-09	97	100	0.0203	203	0.02	11.9	7600	10300	36	13	0.01	0.01	13.2	5.9	17	0.01
KL20-09	100	103	0.0047	47	0.01	3.3	2110	1825	16	0.01	0.01	0.01	2	5.8	15	0.01
KL20-09	103	106	0.0063	63	0.01	5.1	1770	2900	74	7	0.01	0.01	1.6	14.4	29	0.01
KL20-09	106	110.5	0.0117	117	0.01	4.6	1460	1970	73	11	0.01	0.01	1.4	13.3	23	0.01
KL20-09	110.5	113.5	0.0257	257	0.04	13.5	6000	9600	31	28	0.01	0.01	3.6	36.4	18	0.01
KL20-09	113.5	116.5	0.0115	115	0.01	4.3	1440	3000	12	18	0.01	0.01	2	16.8	23	0.01
KL20-09	116.5	119.5	0.0126	126	0.01	5.4	840	2840	15	8	0.01	0.01	2.4	8.2	15	0.01
KL20-09	119.5	122.5	0.0042	42	0.01	3.1	450	1170	3	5	0.01	0.01	0.9	6.5	22	0.01
KL20-09	122.5	125.5	0.027	270	0.02	7.6	610	1250	26	15	0.01	0.01	0.9	16.2	17	0.01
KL20-09	125.5	128.5	0.0206	206	0.02	12.1	378	2450	16	8	10	0.01	1.1	15.5	18	0.01
KL20-09	128.5	131.5	0.0155	155	0.29	5.5	368	550	10	3	92	0.01	0.2	8.7	15	0.01
KL20-09	131.5	134.5	0.0104	104	0.01	1.5	460	450	12	0.01	9	0.01	0.6	6.4	18	0.01
KL20-09	134.5	137.5	0.008	80	0.01	3.2	92	100	63	2	0.01	0.01	1.1	5.3	17	0.01
KL20-09	137.5	140.5	0.0128	128	0.02	4.2	95	132	80	5	1	0.01	1.2	4.8	18	0.01
KL20-09	140.5	143.5	0.0068	68	0.05	5.7	131	125	77	8	1	0.01	0.9	5.3	19	0.01
KL20-09	143.5	146.5	0.0097	97	0.03	5.3	430	490	180	0.01	9	0.01	0.5	6.7	18	0.01
KL20-09	146.5	149.5	0.022	220	0.04	5.2	241	257	170	33	8	0.01	0.3	6.5	30	0.01
KL20-09	149.5	152.5	0.048	480	0.16	11.6	2060	610	370	2	28	0.01	1.6	12.2	27	0.01
KL20-09	152.5	156.8	0.0148	148	0.13	11.3	1410	2200	250	3	3	0.01	0.8	16.9	26	0.01
KL20-09	156.8	160	0.0108	108	0.01	5.3	1210	2360	20	8	13	0.01	1.3	14.1	15	0.01
KL20-09	160	163	0.06	600	0.01	21.8	1730	1780	48	13	64	0.01	1.5	8.6	16	0.01
KL20-09	163	166	0.076	760	0.01	20.6	3610	4200	25	22	55	0.01	2.3	35.2	20	0.01
KL20-09	166	169	0.0204	204	0.01	11.9	440	930	17	13	26	0.01	0.8	4.4	21	0.01
KL20-09	169	173.1	0.01	100	0.01	2.5	600	510	11	17	5	0.01	1	4.3	18	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL20-09	173.1	176.5	0.0138	138	0.1	4.1	1850	720	23	7	10	0.01	0.5	4.4	16	0.01
KL20-09	176.5	179.5	0.02	200	0.08	1.4	590	190	20	2	2	0.01	0.7	1.9	24	0.01
KL20-09	179.5	182.5	0.0158	158	0.1	3.1	4430	2600	19	0.01	6	0.01	2.6	6.4	17	0.01
KL20-09	182.5	185.5	0.0147	147	0.11	1.5	4370	1560	11	0.01	10	0.01	0.7	15.0	22	0.01
KL20-09	185.5	188.5	0.28	2800	0.51	10.5	10200	770	27	0.01	22	8	2.1	31.3	24	0.01
KL20-09	188.5	191.5	0.117	1170	2.68	8.2	4400	580	18	0.01	8	4	1.1	12.1	23	0.01
KL20-09	191.5	194.5	0.29	2900	0.29	5.4	25600	750	9	6	29	6	0.01	20.5	64	0.01
KL20-09	194.5	197.5	0.42	4200	0.17	5.6	17300	260	23	4	227	11	0.9	28.4	41	0.01
KL20-09	197.5	200.5	0.63	6300	0.25	38.3	45100	6000	38	3	102	17	10	27.0	31	0.01
KL20-09	200.5	203.5	0.071	710	0.15	1.8	600	94	27	92	9	0.01	3.5	3.6	54	0.01
KL20-09	203.5	206.5	0.0369	369	0.04	1.7	1790	132	27	1272	7	0.01	1.5	5.7	45	0.01
KL20-09	206.5	209.5	0.158	1580	0.03	1.5	3860	31	36	65	39	4	0.01	12.6	22	0.01
KL20-09	209.5	212.5	0.077	770	0.01	0.6	131	14	1	4	11	5	0.2	5.6	0	0.01
KL20-09	212.5	215.5	0.6	6000	0.11	4.7	7100	103	18	102	7	13	0.7	8.4	19	0.01
KL20-09	215.5	218.5	0.177	1770	0.43	2	25000	230	15	25	4	26	0.01	15.5	19	0.01
KL20-09	218.5	221.5	0.192	1920	0.28	3.1	6400	76	10	21	3	6	1	10.0	13	0.01
KL20-09	221.5	224.5	0.227	2270	0.42	2.7	4300	77	17	10	4	8	0.6	6.8	14	0.01
KL20-09	224.5	227.5	0.117	1170	4.61	3.3	14300	201	28	10	128	11	1	21.4	23	0.01
KL20-09	227.5	230.5	0.28	2800	0.58	3.4	4400	100	21	32	160	8	0.7	10.7	14	0.01
KL20-09	230.5	232.5	0.203	2030	0.33	2	1240	35	26	40	33	14	3.5	9.7	23	0.01
KL20-09	232.5	236.5	0.497	4970	0.34	2.8	3300	44	8	42	50	22	0.4	7.2	5	0.01
KL20-09	236.5	239.5	0.22	2200	0.22	1.9	12000	62	5	148	78	19	1	24.7	5	0.01
KL20-09	239.5	242.5	0.56	5600	1.13	3	13600	34	20	109	80	13	0.7	6.9	20	0.01
KL20-09	242.5	245.5	0.76	7600	1.21	4.3	15400	370	340	175	22	9	1.2	11.6	29	0.35
KL20-09	245.5	248.5	0.472	4720	0.47	1.7	468	36	12	167	42	2	0.6	12.8	28	0.01
KL20-09	248.5	251.5	0.377	3770	0.14	1.4	187	54	25	1330	94	5	0.4	5.6	86	0.01
KL20-09	251.5	254.5	1.13	11300	0.91	5.4	56800	63	20	37	54	38	2.1	98.5	47	0.01
KL20-09	254.5	257.5	0.18	1800	0.07	0.8	870	22	11	560	1	3	0.4	6.4	17	0.01
KL20-09	257.5	260.5	0.522	5220	0.07	3.1	199	72	20	560	48	3	1.5	6.7	29	0.01
KL20-09	260.5	263.5	0.017	170	0.01	0.01	55	14	0.01	550	1	0.01	0.3	2.3	12	0.01
KL20-09	263.5	266.5	0.0173	173	0.04	0.01	660	37	3	114	2	0.01	0.01	5.8	6	0.01
KL20-09	266.5	269.5	0.204	2040	0.04	1.6	193	21	7	244	3	0.01	0.01	4.6	18	0.01
KL20-09	269.5	272.5	0.346	3460	0.16	1.7	105	32	13	770	0.01	0.01	0.4	5.3	37	0.01
KL20-09	272.5	275.5	0.53	5300	0.7	2.7	28500	13	10	19	4	35	0.3	39.5	17	0.01
KL20-09	275.5	278.5	0.166	1660	0.19	1.8	4740	10	10	13	5	24	2	4.8	17	0.01
KL20-09	278.5	281.5	0.471	4710	0.5	4.3	4590	8	8	4	5	35	0.4	5.3	19	0.01
KL20-09	281.5	284.5	0.163	1630	0.29	4.4	650	17	6	7	2	0.01	0.01	0.8	12	0.01
KL20-09	284.5	287.5	0.83	8300	0.68	22.4	2500	30	6	20	3	7	0.01	3.0	16	0.01
KL20-09	287.5	290.5	0.33	3300	0.45	2.4	8000	8	9	6	6	35	0.01	12.4	29	0.01
KL20-09	290.5	293.5	0.114	1140	0.19	0.8	4200	9	2	13	1	21	0.01	5.3	22	0.01
KL20-09	293.5	296.5	2.22	22200	1.82	6	630	12	0.01	11	0.01	64	0.01	22.0	32	0.01
KL20-09	296.5	299.5	0.67	6700	0.53	1.8	265	6	0.01	13	0.01	22	0.01	7.8	24	0.01
KL20-09	299.5	302.5	0.76	7600	0.79	3	286	5	4	54	0.01	32	0.01	10.5	26	0.01
KL20-09	302.5	305.5	0.144	1440	0.15	0.01	96	7	2	92	0.01	7	0.01	2.4	28	0.01
KL20-09	305.5	308.5	0.242	2420	0.24	0.8	78	6	0.01	334	0.01	7	0.01	4.3	42	0.01
KL20-09	308.5	311.5	0.39	3900	0.34	1	63	7	0.01	32	0.01	5	0.01	5.5	13	0.01
KL20-09	311.5	314.5	1.05	10500	0.94	2.1	216	7	0.01	16	0.01	24	0.01	10.8	24	0.01
KL20-09	314.5	316.2	0.081	810	0.11	0.01	166	27	0.01	740	0.01	15	0.3	2.3	24	0.01
KL20-09	316.2	319	2.29	22900	2.89	4.6	530	19	0.01	194	0.01	44	0.2	26.0	60	0.01
KL20-09	319	322	3.62	36200	6.1	7	440	14	0.01	53	0.01	78	0.5	24.0	31	0.01
KL20-09	322	324.7	2.04	20400	3.01	3.6	160	23	0.01	12	0.01	41	1	19.5	45	0.01
KL20-09	324.7	326.9	0.96	9600	0.78	3.1	75	12	0.01	760	0.01	14	0.01	8.2	64	0.01
KL20-09	326.9	328.6	1.28	12800	1.02	3.2	98	17	3	31	0.01	29	0.01	11.8	123	0.01
KL20-09	328.6	331	1.27	12700	1.32	2.4	126	14	0.01	65	0.01	57	0.01	10.0	64	0.1
KL20-09	331	334	1.51	15100	1.15	3.9	690	650	59	85	0.01	44	8.3	13.8	90	0.1
KL20-09	334	336.1	0.65	6500	0.37	1.6	37	20	14	210	0.01	14	0.2	8.3	96	0.01
KL20-09	336.1	337.9	0.6	6000	0.25	2.1	156	18	12	220	0.01	5	0.01	5.7	136	0.01
KL20-09	337.9	340	0.369	3690	0.23	1.8	157	126	5	153	1	14	0.4	8.8	98	0.01
KL20-09	340	341.2	0.24	2400	0.38	0.8	47	13	2	204	0.01	6	0.5	4.0	95	0.01
KL20-09	341.2	343	0.62	6200	0.28	3	173	88	7	113	2	11	0.9	16.0	106	0.01
KL20-09	343	346	0.61	6100	0.63	1.2	127	23	10	112	0.01	6	0.01	8.4	185	0.01
KL20-09	346	349	0.6	6000	0.56	1.5	69	14	5	132	0.01	12	0.2	7.8	126	0.01
KL20-09	349	352	0.62	6200	0.62	1.4	61	13	1	260	1	11	0.6	6.8	141	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL20-09	352	355	0.67	6700	0.59	3.5	990	341	26	56	14	6	5.3	6.3	103	0.1
KL20-09	355	358	0.45	4500	0.39	2	196	168	88	27	2	2	13.9	6.3	115	0.46
KL20-09	358	361	0.58	5800	0.61	1.5	103	15	51	63	1	9	0.8	5.5	117	0.01
KL20-09	361	364	0.42	4200	0.54	0.9	76	23	20	18	1	6	0.6	7.0	123	0.01
KL20-09	364	367	0.451	4510	0.57	0.9	61	16	3	34	0.01	7	0.6	6.3	130	0.01
KL20-09	367	370	0.82	8200	0.94	1.7	78	17	0.01	45	0.01	10	0.01	8.5	143	0.01
KL20-09	370	373	0.58	5800	0.45	1.3	107	27	77	51	0.01	11	3.7	8.0	121	0.2
KL20-09	373	376	0.495	4950	0.35	1.4	108	25	38	61	0.01	6	2.1	5.5	107	0.01
KL20-09	376	379	0.38	3800	0.32	1.4	87	24	47	121	0.01	7	4.5	8.0	98	0.11
KL20-09	379	382	0.476	4760	0.33	1.1	51	13	17	28	0.01	7	0.4	5.8	96	0.01
KL20-09	382	385	0.55	5500	0.5	1	52	10	4	67	0.01	7	0.7	5.2	102	0.01
KL20-09	385	388	0.37	3700	0.56	1	68	21	4	167	0.01	11	0.8	6.0	79	0.01
KL20-09	388	391	0.357	3570	0.29	0.9	90	36	4	36	0.01	10	0.01	4.8	104	0.01
KL20-09	391	394	0.54	5400	0.57	1	48	13	0.01	38	0.01	7	0.3	4.8	125	0.01
KL20-09	394	397	0.43	4300	0.29	1.4	54	10	1	53	0.01	9	0.01	3.7	87	0.01
KL20-09	397	400	0.4	4000	0.27	1.4	60	17	2	58	0.01	10	0.01	4.5	86	0.01
KL20-09	400	403	0.489	4890	0.32	1.4	57	8	0.01	72	1	13	0.01	6.3	90	0.01
KL20-09	403	406	0.479	4790	0.39	1.6	64	6	0.01	71	0.01	17	0.01	6.9	91	0.01
KL20-09	406	409	0.57	5700	0.37	1.4	83	11	3	28	1	13	0.6	8.9	76	0.01
KL20-09	409	412	0.43	4300	0.36	0.9	66	10	1	57	0.01	13	0.01	6.0	75	0.01
KL20-09	412	415	0.5	5000	0.32	1.3	76	24	30	76	0.01	11	1.1	6.8	84	0.01
KL20-09	415	418	0.4	4000	0.37	2.1	189	670	30	96	0.01	13	2.4	5.5	75	0.01
KL20-09	418	421	0.38	3800	0.28	1	59	22	3	48	0.01	12	0.4	8.4	38	0.01
KL20-09	421	424	0.273	2730	0.22	0.8	268	149	280	29	0.01	9	4.4	4.5	39	0.01
KL20-09	424	427	0.436	4360	0.36	1.2	253	127	65	41	0.01	13	5.1	6.1	54	0.01
KL20-09	427	430	0.439	4390	0.29	1	52	15	2	107	0.01	17	0.01	5.0	52	0.01
KL20-09	430	433	0.54	5400	0.54	1.2	34	16	32	19	0.01	13	3.2	4.5	52	0.01
KL20-09	433	436	0.86	8600	0.57	2	84	14	2	176	0.01	38	0.4	3.0	64	0.01
KL20-09	436	439	1.04	10400	0.76	2.2	83	17	12	91	0.01	27	0.01	6.5	56	0.01
KL20-09	439	442	0.58	5800	0.48	1.2	55	10	2	193	0.01	22	0.01	3.2	56	0.01
KL20-09	442	445	1.25	12500	0.89	2.6	76	11	1	92	0.01	30	0.3	5.3	64	0.01
KL20-09	445	448	1.04	10400	0.76	2.3	61	15	7	61	0.01	26	0.5	4.3	63	0.01
KL20-09	448	449.8	0.615	6150	0.44	1.3	72	15	2	239	0.01	31	0.01	5.6	75	0.01
KL20-09	449.8	451.6	0.6	6000	0.32	1.7	72	19	2	210	0.01	30	0.4	7.0	71	0.01
KL20-09	451.6	454	0.89	8900	0.65	3	79	16	1	232	1	21	0.3	9.5	71	0.01
KL20-09	454	457	1.36	13600	1.4	2.8	150	34	47	43	0.01	27	2.8	11.0	57	0.01
KL20-09	457	460	0.615	6150	0.68	1.6	196	53	52	11	1	12	7.4	4.8	116	0.01
KL20-09	460	463	1.39	13900	1.92	7.2	286	59	480	5	2	20	22.5	3.0	92	1.18
KL20-09	463	466	1.55	15500	2.24	3.5	62	11	4	4	2	17	0.6	9.0	52	0.1
KL20-09	466	469	1.15	11500	1.25	2.4	80	18	60	13	0.01	13	6.2	6.3	38	0.1
KL20-09	469	472	0.83	8300	0.74	1.9	95	13	5	36	0.01	27	0.5	6.3	43	0.01
KL20-09	472	474.2	1.54	15400	2.04	3.8	125	16	6	22	1	27	0.3	7.5	86	0.11
KL20-09	474.2	475.6	0.84	8400	0.51	2.9	140	18	7	69	0.01	17	0.2	10.2	48	0.01
KL20-09	475.6	478	0.52	5200	0.8	1.6	52	14	66	23	2	6	5.6	5.8	41	0.01
KL20-09	478	481	0.74	7400	0.88	1.6	40	7	3	23	0.01	13	0.4	6.8	283	0.01
KL20-09	481	484	0.57	5700	0.75	1.3	38	8	21	21	0.01	5	0.3	4.8	300	0.01
KL20-09	484	487	0.425	4250	0.5	4.4	70	38	60	20	0.01	7	27	3.3	270	0.1
KL20-09	487	490	0.6	6000	0.54	1.3	53	13	26	27	0.01	10	0.4	4.5	63	0.01
KL20-09	490	493	0.64	6400	0.68	3.4	56	19	280	23	0.01	9	15.7	4.8	54	0.15
KL20-09	493	496	0.64	6400	1.09	3.2	51	18	320	18	1	6	9	5.3	50	0.16
KL20-09	496	499	0.44	4400	0.64	2.6	38	10	110	11	1	5	6.7	5.5	37	0.1
KL20-09	499	502	0.77	7700	0.5	2.2	72	10	3	420	0.01	18	0.4	5.6	56	0.01
KL20-09	502	505	0.72	7200	0.62	1.8	63	14	22	35	0.01	15	3	3.5	76	0.01
KL20-09	505	508	0.357	3570	0.34	3.4	58	33	39	19	0.01	7	26	5.2	62	0.12
KL20-09	508	511	0.5	5000	0.5	4.6	72	30	66	11	0.01	8	30	5.5	189	0.24
KL20-09	511	514	0.66	6600	0.47	23.1	264	164	800	31	0.01	12	110	6.3	175	1.72
KL20-09	514	517	0.73	7300	0.52	1.6	48	59	19	24	0.01	6	1.5	4.2	217	0.01
KL20-09	517	520	0.335	3350	0.34	0.7	27	10	38	12	0.01	3	0.6	2.8	154	0.01
KL20-09	520	523	0.426	4260	0.34	3	75	76	78	13	0.01	7	15	3.3	220	0.12
KL20-09	523	526	0.414	4140	0.45	1	33	14	48	10	0.01	5	2.7	3.5	266	0.18
KL20-09	526	529	0.46	4600	0.43	1.3	32	11	45	10	0.01	4	3.8	2.5	202	0.11
KL20-09	529	532	0.44	4400	0.53	2.6	39	33	62	11	0.01	6	16.2	3.5	251	0.79
KL20-09	532	535	0.5	5000	0.41	1.2	35	5	75	12	0.01	4	3.6	2.5	235	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL20-09	535	538	0.482	4820	0.51	1.2	59	20	21	12	0.01	5	1.8	3.3	217	0.01
KL20-09	538	541	0.324	3240	0.29	0.6	36	7	2	39	0.01	9	0.01	3.5	210	0.01
KL20-09	541	544	0.225	2250	0.24	0.6	38	10	0.01	13	0.01	7	0.01	3.0	185	0.01
KL20-09	544	547	0.346	3460	0.53	1.1	49	10	5	12	0.01	5	0.01	3.5	176	0.01
KL20-09	547	550	0.321	3210	0.38	1.3	25	9	4	13	1	6	0.01	4.2	174	0.01
KL20-09	550	553	0.5	5000	0.62	1.2	27	5	0.01	10	0.01	7	0.01	3.3	181	0.01
KL20-09	553	556	0.35	3500	0.39	0.8	31	8	3	12	0.01	8	0.01	3.5	61	0.01
KL20-09	556	559	0.35	3500	0.11	0.8	41	10	44	18	0.01	8	0.7	3.3	286	0.01
KL20-09	559	562	0.152	1520	0.08	0.8	38	35	65	9	0.01	5	1.1	2.5	220	0.01
KL20-09	562	565	0.58	5800	0.44	1	30	14	17	13	0.01	6	0.01	3.3	48	0.01
KL20-09	565	568	0.498	4980	0.43	0.9	27	9	20	14	0.01	7	0.01	3.8	182	0.01
KL20-09	568	570.3	0.334	3340	0.33	0.8	20	7	2	10	0.01	6	0.01	2.5	257	0.01
KL20-09	570.3	572.5	0.376	3760	0.33	0.7	17	5	0.01	15	0.01	5	0.01	3.5	305	0.01
KL20-09	572.5	575.5	0.491	4910	0.24	1.7	27	10	33	12	0.01	12	0.7	5.5	207	0.01
KL20-09	575.5	578.5	0.186	1860	0.13	0.01	25	9	13	25	0.01	6	0.01	2.8	237	0.01
KL20-09	578.5	581.5	0.22	2200	0.17	0.5	20	6	34	31	0.01	4	1.1	2.5	141	0.01
KL20-09	581.5	584.5	0.215	2150	0.14	1.1	26	15	41	16	0.01	5	1.1	2.7	151	0.01
KL20-09	584.5	587.5	0.26	2600	0.26	0.7	24	8	35	52	0.01	3	1.6	2.3	145	0.01
KL20-09	587.5	590.3	0.456	4560	0.32	1.1	30	8	5	34	0.01	6	1.6	4.3	170	0.01
KL20-09	590.3	593.4	0.63	6300	0.48	1.7	51	5	46	53	0.01	10	0.01	5.3	189	0.1
KL20-09	593.4	596.5	0.486	4860	0.37	1.8	65	7	75	26	0.01	11	3.1	4.8	175	0.01
KL20-09	596.5	599.5	0.477	4770	0.25	1	40	0.01	59	32	0.01	10	1.9	3.8	237	0.01
KL20-09	599.5	602.5	0.41	4100	0.29	1.4	38	0.01	6	15	0.01	10	0.01	3.5	216	0.01
KL20-09	602.5	605.5	0.423	4230	0.29	1.1	41	8	10	34	0.01	9	0.01	4.3	221	0.01
KL20-09	605.5	608.5	0.383	3830	0.29	1.6	166	30	83	31	0.01	7	12.4	5.3	214	0.1
KL20-09	608.5	611.5	0.044	440	0.04	0.01	58	18	11	57	1	15	0.01	6.5	158	0.01
KL20-09	611.5	614.5	0.272	2720	0.19	0.01	14	0.01	6	60	0.01	6	0.01	3.3	190	0.01
KL20-09	614.5	617.5	0.225	2250	0.16	0.6	15	12	30	30	1	5	2.6	4.0	178	0.01
KL20-09	617.5	620.5	0.138	1380	0.11	0.01	12	8	5	19	0.01	5	0.01	2.8	173	0.01
KL20-09	620.5	623.5	0.51	5100	0.43	1	25	8	52	18	0.01	8	1.6	3.8	203	0.01
KL20-09	623.5	626.5	0.375	3750	0.34	1	29	15	16	17	0.01	5	0.4	3.3	241	0.01
KL20-09	626.5	629.5	0.34	3400	0.29	0.7	26	7	8	23	0.01	7	0.5	3.5	224	0.01
KL20-09	629.5	632.5	0.283	2830	0.12	0.01	20	7	10	42	0.01	4	0.01	3.8	129	0.01
KL20-09	632.5	635.5	0.6	6000	0.42	2.3	52	25	63	13	0.01	3	20.4	4.8	159	0.69
KL20-09	635.5	638.5	0.278	2780	0.13	0.6	33	14	8	26	0.01	6	0.4	3.0	153	0.01
KL20-09	638.5	641.5	0.23	2300	0.12	0.6	59	42	9	24	0.01	3	1	2.9	60	0.01
KL20-09	641.5	643.1	0.245	2450	0.12	0.6	69	64	3	12	0.01	2	0.8	3.1	65	0.01
KL20-09	643.1	645.2	0.25	2500	0.12	0.7	133	158	3	65	0.01	0.01	1.1	2.4	56	0.01
KL22-02	230.6	234.4	0.15	1500	0.09	4	8400	5900	21	460	9	2	1.8	12.3	72	0.01
KL22-02	234.4	235.8	0.54	5400	1.99	2.2	106800	115	8	7	94	90	1	41.4	31	0.01
KL22-02	235.8	238.7	0.54	5400	0.59	4.2	19200	147	6	8	40	34	0.6	80.0	22	0.01
KL22-02	238.7	240.7	1.06	10600	1.24	1.5	167	37	3	25	14	7	0.4	14.8	30	0.01
KL22-02	240.7	242	1.3	13000	1.56	1.7	430	41	8	60	8	25	0.2	21.0	34	0.01
KL22-02	242	243.5	2.74	27400	4.07	6.8	1150	134	3	4	25	65	0.2	58.8	23	0.1
KL22-02	243.5	245.5	0.97	9700	2.68	2.4	89	60	16	5	14	6	0.3	7.8	27	0.01
KL22-02	245.5	248	0.65	6500	1.38	0.8	600	25	10	249	18	3	0.4	7.5	26	0.01
KL22-02	248	251	0.247	2470	0.95	0.01	39	19	5	870	6	0.01	0.3	4.5	31	0.01
KL22-02	251	254	0.3	3000	0.94	0.01	257	40	16	480	7	3	0.8	5.3	36	0.01
KL22-02	254	257	0.149	1490	0.3	0.01	92	17	18	690	5	2	0.5	4.2	30	0.01
KL22-02	257	260	0.22	2200	0.71	0.01	74	17	11	570	5	4	0.3	3.5	47	0.01
KL22-02	260	263	0.36	3600	0.45	1.1	195	14	6	196	3	7	0.01	4.2	23	0.01
KL22-02	263	266	0.123	1230	0.21	0.01	55	14	11	775	0.01	5	0.2	3.0	28	0.01
KL22-02	266	269	0.0175	175	0.03	0.01	47	10	8	375	0.01	2	0.2	0.6	19	0.01
KL22-02	269	272	0.0169	169	0.04	0.01	41	9	19	520	0.01	0.01	0.01	1.4	12	0.01
KL22-02	272	275	0.0218	218	0.04	0.01	63	11	7	373	0.01	3	0.3	3.4	20	0.01
KL22-02	275	278	0.047	470	0.08	0.01	1270	124	19	176	2	2	0.7	4.1	27	0.01
KL22-02	278	281.2	0.46	4600	0.19	1.5	207	70	17	266	8	10	1.3	8.3	44	0.01
KL22-02	281.2	284.2	0.57	5700	0.83	1.2	690	12	7	13	22	19	0.01	5.3	21	0.01
KL22-02	284.2	286.8	0.58	5800	1.23	0.01	3600	13	5	32	2	36	0.01	8.5	25	0.01
KL22-02	286.8	288.8	0.0163	163	0.02	0.01	30	7	8	45	0.01	0.01	0.01	1.4	19	0.01
KL22-02	288.8	290.4	0.127	1270	0.09	0.01	42	12	4	410	1	0.01	0.01	2.4	16	0.01
KL22-02	290.4	293.4	0.7	7000	3.07	4.3	7800	21	8	5	1	31	0.01	8.0	29	0.01
KL22-02	293.4	296.5	0.62	6200	0.68	2.9	4400	25	18	5	1	33	0.01	11.3	38	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL22-02	296.5	299.4	0.28	2800	0.32	2.2	3100	42	9	5	12	15	0.4	4.8	18	0.01
KL22-02	299.4	302.4	0.088	880	0.17	0.5	2180	11	9	22	0.01	6	0.5	1.5	17	0.01
KL22-02	302.4	304.7	0.0238	238	0.03	0.01	730	10	15	3	0.01	12	0.2	0.6	11	0.01
KL22-02	304.7	306.7	1.42	14200	0.88	1.3	186	7	1	5	1	26	0.3	14.0	15	0.01
KL22-02	306.7	308	1.28	12800	1.41	1.4	93	8	0.01	4	1	20	0.01	13.0	22	0.01
KL22-02	308	311	0.89	8900	0.36	0.01	116	8	1	75	0.01	32	0.01	11.2	13	0.01
KL22-02	311	314	3.15	31500	1.76	6.2	108	11	2	62	4	40	0.01	26.3	53	0.01
KL22-02	314	317	0.318	3180	0.31	0.01	99	8	0.01	149	1	23	0.01	5.0	50	0.01
KL22-02	317	320.7	0.68	6800	0.56	0.01	92	18	4	92	0.01	21	0.3	9.3	57	0.01
KL22-02	320.7	323	2.57	25700	2.64	4.2	111	13	5	42	1	26	0.2	26.3	39	0.01
KL22-02	323	325.2	2.17	21700	1.98	2.7	264	54	12	56	1	25	0.3	15.7	91	0.01
KL22-02	325.2	328.2	0.737	7370	0.51	1.4	141	78	11	13	4	15	0.5	9.7	65	0.01
KL22-02	328.2	330.8	2.07	20700	1.22	3	115	23	17	66	2	24	0.6	31.0	36	0.01
KL22-02	330.8	334.1	1.95	19500	1.76	3.8	61	27	7	21	3	13	0.4	18.0	50	0.01
KL22-02	334.1	336.6	1.76	17600	1.25	2.8	100	10	7	71	1	16	0.3	11.0	67	0.01
KL22-02	336.6	339.1	0.55	5500	0.62	2.2	162	78	20	32	2	8	10.4	6.3	76	0.01
KL22-02	339.1	341	0.5	5000	0.67	0.01	30	37	5	29	0.01	7	0.5	6.0	65	0.01
KL22-02	341	344	0.83	8300	0.8	0.8	73	12	7	45	0.01	12	0.3	7.5	84	0.01
KL22-02	344	347	1.2	12000	0.61	2.5	91	28	12	16	1	12	0.7	7.7	74	0.01
KL22-02	347	350	0.62	6200	0.56	3.3	1470	1240	23	20	4	10	6.2	8.0	60	0.01
KL22-02	350	353	0.73	7300	0.49	0.5	55	17	8	61	1	10	0.3	7.5	64	0.01
KL22-02	353	356	0.57	5700	0.31	0.01	54	12	12	33	0.01	10	0.3	7.8	57	0.01
KL22-02	356	359	0.85	8500	0.41	0.01	58	12	8	64	1	12	0.4	6.3	67	0.01
KL22-02	359	362	0.64	6400	0.73	0.01	45	8	2	38	0.01	8	0.2	7.8	65	0.01
KL22-02	362	365	0.77	7700	0.6	0.01	61	10	2	50	0.01	14	0.2	5.5	75	0.01
KL22-02	365	368	0.486	4860	0.38	0.01	65	8	12	79	0.01	11	0.6	7.0	51	0.01
KL22-02	368	371	0.45	4500	0.34	0.01	41	10	6	251	0.01	8	0.2	5.4	77	0.01
KL22-02	371	374	0.72	7200	0.87	2.1	52	10	4	106	0.01	11	0.2	6.5	65	0.01
KL22-02	374	377	0.391	3910	0.26	0.01	40	8	3	31	0.01	10	0.5	6.3	84	0.01
KL22-02	377	380	0.84	8400	0.56	2	74	11	4	60	1	21	1.4	9.4	64	0.01
KL22-02	380	383	0.3	3000	0.19	0.01	40	9	3	43	0.01	10	0.4	7.5	75	0.01
KL22-02	383	386	0.458	4580	0.31	0.01	71	26	4	25	0.01	19	0.4	5.5	70	0.01
KL22-02	386	389	0.375	3750	0.24	0.01	38	8	6	68	0.01	15	0.3	7.0	99	0.01
KL22-02	389	392	0.59	5900	0.35	1.3	84	17	69	54	0.01	18	3.8	7.0	72	0.01
KL22-02	392	395	0.585	5850	0.36	0.7	45	7	2	112	0.01	19	0.3	7.0	78	0.01
KL22-02	395	398	0.85	8500	0.58	2	65	8	2	360	0.01	34	0.3	9.3	66	0.01
KL22-02	398	401	0.28	2800	0.24	0.01	39	7	3	59	0.01	18	0.2	3.8	84	0.01
KL22-02	401	404	0.352	3520	0.48	0.01	42	10	3	87	0.01	9	0.2	4.8	70	0.01
KL22-02	404	407	0.38	3800	0.24	0.01	76	14	2	263	0.01	10	0.01	5.8	115	0.01
KL22-02	407	410	0.39	3900	0.19	0.01	40	10	2	139	0.01	10	0.01	4.8	77	0.01
KL22-02	410	413	0.45	4500	0.26	0.01	42	9	2	80	1	12	0.01	4.8	63	0.01
KL22-02	413	416.2	0.69	6900	0.57	0.01	59	10	5	44	0.01	25	0.01	4.8	78	0.01
KL22-02	416.2	419	0.42	4200	0.35	1.1	74	9	62	20	0.01	10	3.2	2.8	81	0.01
KL22-02	419	422	0.64	6400	0.7	0.01	59	10	3	10	1	12	0.01	4.2	91	0.01
KL22-02	422	423.6	0.42	4200	0.46	0.01	52	10	1	8	0.01	12	0.01	3.5	84	0.01
KL22-02	423.6	425.2	0.64	6400	0.45	0.01	55	9	4	12	0.01	11	0.01	5.5	66	0.01
KL22-02	425.2	428	0.68	6800	0.61	0.01	65	9	48	10	0.01	11	0.4	5.1	88	0.01
KL22-02	428	431	0.73	7300	0.8	1.3	60	10	8	11	2	7	0.5	5.0	88	0.01
KL22-02	431	434	0.52	5200	0.66	0.01	53	9	10	9	1	4	0.01	4.0	97	0.01
KL22-02	434	437	0.85	8500	0.83	0.01	85	10	110	91	0.01	14	5.1	6.8	90	0.12
KL22-02	437	440	1.1	11000	0.83	1.4	89	10	26	118	0.01	17	0.5	6.5	85	0.01
KL22-02	440	443	1.31	13100	0.99	1.5	81	10	2	169	0.01	20	0.2	5.8	62	0.01
KL22-02	443	444.9	1.47	14700	1.53	2.5	79	9	0.01	38	2	16	0.01	7.0	61	0.01
KL22-02	444.9	447.6	2.42	24200	1.28	4.8	121	11	2	70	0.01	19	0.01	9.0	74	0.01
KL22-02	447.6	449	2.12	21200	0.78	5.2	101	12	6	11	0.01	27	0.01	8.8	98	0.01
KL22-02	449	452	0.98	9800	0.48	3	48	15	7	82	1	16	0.01	10.8	148	0.01
KL22-02	452	455.2	0.63	6300	0.43	0.7	62	14	5	68	0.01	16	0.2	7.5	98	0.01
KL22-02	455.2	458	0.86	8600	0.57	1.3	130	14	58	64	0.01	12	0.8	7.4	135	0.01
KL22-02	458	461	0.67	6700	0.48	1.2	48	11	25	49	0.01	11	1.6	6.0	221	0.01
KL22-02	461	464	0.39	3900	0.47	0.7	45	11	5	8	0.01	6	0.01	5.1	240	0.01
KL22-03	277	279.5	0.36	3600	0.29	2.3	241	9	5	0.01	0.01	14	0.01	5.8	15	0.01
KL22-03	279.5	281.75	1.66	16600	2.22	15.8	7800	13	1	3	4	32	0.01	17.7	17	0.01
KL22-03	281.75	283.9	0.46	4600	0.73	3.6	2320	14	3	15	2	70	0.4	9.0	34	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL22-03	283.9	286.9	0.58	5800	0.81	4.7	114	10	2	43	1	14	0.2	8.5	20	0.01
KL22-03	286.9	289.55	1.26	12600	1.49	3.4	83	14	14	12	1	14	0.01	11.2	53	0.01
KL22-03	289.55	292.55	3.42	34200	2.01	9.8	195	12	6	17	2	21	0.2	19.5	76	0.01
KL22-03	292.55	295.65	1.44	14400	0.9	4.3	165	10	5	224	4	13	0.01	13.0	24	0.01
KL22-03	295.65	298.65	0.56	5600	0.39	2.3	112	8	5	10	5	5	0.01	8.5	49	0.01
KL22-03	298.65	301.7	0.43	4300	0.33	1.1	52	11	6	27	1	7	0.2	9.3	56	0.01
KL22-03	301.7	303.1	0.6	6000	0.6	2	53	6	2	22	0.01	9	0.01	8.8	20	0.01
KL22-03	303.1	306.4	1.25	12500	0.47	1.8	83	6	3	990	0.01	23	0.2	7.0	48	0.01
KL22-03	306.4	308.6	0.38	3800	0.18	1.2	36	8	4	102	0.01	10	0.2	2.5	98	0.01
KL22-03	308.6	310.6	0.5	5000	0.18	2.6	42	9	2	113	0.01	9	0.01	6.8	73	0.01
KL22-03	310.6	312.45	0.6	6000	0.25	1.8	47	8	3	271	0.01	13	0.2	7.0	77	0.01
KL22-03	312.45	314.5	1.07	10700	0.48	1.6	70	9	2	348	0.01	12	0.2	5.5	117	0.01
KL22-03	314.5	316.2	0.56	5600	0.3	1	43	10	2	900	0.01	27	0.2	11.3	139	0.01
KL22-03	316.2	318.65	0.7	7000	0.34	1.2	51	14	2	75	0.01	18	0.01	6.0	83	0.01
KL22-03	318.65	321	0.66	6600	0.42	0.8	42	5	3	76	0.01	10	0.6	4.0	94	0.01
KL22-03	321	324	0.64	6400	0.53	0.9	48	6	3	34	0.01	13	0.3	5.9	68	0.01
KL22-03	324	327	1.02	10200	0.78	1.5	54	8	2	30	0.01	18	0.2	4.3	74	0.01
KL22-03	327	330.25	1.87	18700	1	2.5	82	9	4	26	0.01	21	0.01	3.3	150	0.01
KL22-03	330.25	333.25	0.9	9000	0.72	0.9	68	12	82	48	0.01	15	0.4	4.3	99	0.01
KL22-03	333.25	336	1.02	10200	0.98	1.2	50	11	3	52	0.01	13	0.01	3.8	101	0.01
KL22-03	336	337.6	1.1	11000	0.89	2.2	65	11	3	124	0.01	15	0.01	4.3	73	0.01
KL22-03	337.6	340.6	0.98	9800	0.66	1.6	50	10	1	25	0.01	13	0.2	3.0	85	0.01
KL22-03	340.6	343.1	0.83	8300	0.3	1.7	149	21	4	35	0.01	10	0.6	6.5	87	0.01
KL22-03	343.1	345	0.84	8400	0.63	1.5	175	25	3	138	1	12	0.3	6.6	112	0.01
KL22-03	345	348	1.02	10200	0.61	1.4	67	13	8	14	0.01	15	0.01	5.5	104	0.01
KL22-03	348	351	0.67	6700	0.48	1.2	263	54	210	41	0.01	14	3.2	3.8	111	0.32
KL22-03	351	354	0.59	5900	0.31	1.4	900	460	570	34	0.01	13	38	4.3	73	1.2
KL22-03	354	357	0.505	5050	0.37	0.9	300	223	190	46	0.01	13	3.7	4.0	91	0.16
KL22-03	357	360.15	0.61	6100	0.45	1.3	67	11	2	11	0.01	13	0.2	3.5	112	0.01
KL22-03	360.15	363.15	0.53	5300	0.24	1.3	50	20	4	32	0.01	12	0.3	5.3	94	0.01
KL22-03	363.15	366.15	0.58	5800	0.34	1.2	44	15	3	14	0.01	12	0.01	4.5	105	0.01
KL22-03	366.15	369.15	0.55	5500	0.36	1.5	42	15	2	36	1	15	0.01	4.5	101	0.01
KL22-03	369.15	372.15	0.5	5000	0.3	1.8	195	36	4	38	1	13	0.4	5.5	99	0.01
KL22-03	372.15	375.15	0.51	5100	0.42	2.4	530	154	6	10	1	13	0.3	5.0	107	0.01
KL22-03	375.15	378	0.92	9200	0.48	6.1	6900	2200	28	4	1	16	2.3	8.5	74	0.01
KL22-03	378	380.5	0.71	7100	0.47	13.2	16300	6700	60	84	0.01	13	16	10.7	64	0.33
KL22-03	380.5	383	0.91	9100	0.68	9.1	1840	1100	41	75	1	11	17.4	11.2	77	0.14
KL22-03	383	386	0.69	6900	0.44	5.3	960	450	7	76	0.01	12	1.9	4.8	89	0.01
KL22-03	386	389	0.93	9300	0.54	2.4	97	37	9	134	0.01	15	1	4.8	82	0.01
KL22-03	389	392.4	0.93	9300	0.91	1.7	68	17	6	98	0.01	14	0.2	5.8	111	0.01
KL22-03	392.4	395.4	3.35	33500	2.86	3.7	138	36	7	41	1	12	0.01	3.5	109	0.01
KL22-03	395.4	397.9	0.66	6600	0.42	0.01	50	12	5	76	0.01	5	0.01	5.7	94	0.01
KL22-03	397.9	399.7	0.143	1430	0.14	0.01	179	16	7	10	0.01	5	0.01	11.1	91	0.01
KL22-04	264	266.4	0.32	3200	0.21	0.01	76	7	0.01	2	0.01	40	0.01	3.0	11	0.01
KL22-04	266.4	269.9	0.81	8100	0.55	1.9	107	10	0.01	16	0.01	11	0.01	8.8	15	0.01
KL22-04	269.9	271.6	1.11	11100	0.77	1	120	18	1	2	0.01	18	0.01	13.5	13	0.01
KL22-04	271.6	275.1	2.56	25600	1.56	3.7	136	8	0.01	2	0.01	32	0.01	25.2	19	0.01
KL22-04	275.1	276	0.77	7700	0.63	2.9	139	6	2	0.01	1	36	0.01	12.3	23	0.01
KL22-04	276	278	0.84	8400	0.56	2.1	118	15	4	5	0.01	21	0.01	12.5	14	0.01
KL22-04	278	280.4	1.03	10300	0.67	2.1	111	8	4	2	0.01	24	0.01	15.7	17	0.01
KL22-04	280.4	283.4	0.88	8800	0.58	2.6	81	0.01	2	128	0.01	12	0.01	7.3	19	0.01
KL22-04	283.4	286.6	1.72	17200	1.09	3.5	108	0.01	2	61	0.01	10	0.01	9.8	16	0.01
KL22-04	286.6	289.6	0.84	8400	0.6	2.2	71	0.01	1	6	1	7	0.01	8.2	15	0.01
KL22-04	289.6	292.6	0.74	7400	0.34	1.8	84	5	3	12	1	11	0.01	4.5	17	0.01
KL22-04	292.6	295.6	0.9	9000	0.46	2.1	68	6	1	14	0.01	14	0.01	8.0	48	0.01
KL22-04	295.6	298.6	1.04	10400	0.49	3.3	89	0.01	1	8	1	14	0.01	7.0	31	0.01
KL22-04	298.6	300.6	0.9	9000	0.36	2.7	113	5	2	14	3	19	0.01	12.3	37	0.01
KL22-04	300.6	302.6	2.05	20500	1.16	3.5	180	57	5	22	2	11	0.2	11.5	20	0.01
KL22-04	302.6	304.6	2.58	25800	1.08	4.2	143	9	1	27	2	19	0.01	7.5	24	0.01
KL22-04	304.6	306.6	0.98	9800	0.3	1.7	83	7	2	104	0.01	17	0.01	9.3	78	0.01
KL22-04	306.6	309.2	0.69	6900	0.5	1.5	34	6	2	152	0.01	8	0.2	6.7	103	0.01
KL22-04	309.2	310.7	0.95	9500	0.35	2.3	50	0.01	0.01	71	0.01	21	0.01	9.0	72	0.01
KL22-04	310.7	313.6	0.96	9600	0.53	2	55	0.01	0.01	64	0.01	10	0.4	2.8	116	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL22-04	313.6	316.6	1.16	11600	0.78	2.2	950	299	6	34	0.01	9	0.6	5.0	137	0.01
KL22-04	316.6	319.6	0.84	8400	0.51	2.3	770	231	5	37	0.01	10	1.8	6.0	123	0.01
KL22-04	319.6	322.6	0.9	9000	0.85	1.6	33	20	1	38	1	9	0.01	5.5	133	0.01
KL22-04	322.6	325.6	1.01	10100	0.52	2	100	40	7	129	0.01	11	2	5.0	89	0.01
KL22-04	325.6	328.6	0.99	9900	0.62	2	156	82	9	124	0.01	10	7.6	4.8	93	0.01
KL22-04	328.6	331.6	0.71	7100	0.58	1.4	45	9	3	89	0.01	11	0.01	5.3	97	0.01
KL22-04	331.6	332.6	1	10000	0.72	1.8	68	8	1	20	0.01	9	0.01	5.3	70	0.01
KL22-04	332.6	336	1	10000	0.84	1.7	39	10	3	71	0.01	8	0.01	4.3	80	0.01
KL22-04	336	339	0.73	7300	0.81	1.6	43	11	2	93	1	10	0.3	5.1	87	0.01
KL22-04	339	342	1.02	10200	0.84	2.1	37	10	1	90	1	9	0.3	5.3	79	0.01
KL22-04	342	345	0.77	7700	0.5	1.8	50	11	0.01	52	0.01	8	0.01	2.5	63	0.01
KL22-04	345	348	0.4	4000	0.29	2.2	2150	86	51	6	2	12	1.3	2.3	45	0.01
KL22-04	348	351	0.85	8500	0.49	2.4	71	13	2	418	0.01	14	0.01	5.8	82	0.01
KL22-04	351	354	0.87	8700	0.42	2.3	73	12	2	130	0.01	12	0.4	5.3	78	0.01
KL22-04	354	357	0.7	7000	0.36	1.8	65	17	3	140	0.01	17	0.2	5.0	73	0.01
KL22-04	357	360	0.45	4500	0.18	1.3	40	12	2	210	0.01	15	0.01	5.0	54	0.01
KL22-04	360	363	1.21	12100	0.57	2.2	87	13	3	55	0.01	18	0.01	5.0	68	0.01
KL22-04	363	366	1.05	10500	0.7	2.3	161	51	19	146	0.01	17	5.2	6.2	82	0.01
KL22-04	366	369	0.79	7900	0.39	2.9	281	70	12	191	0.01	19	4	6.5	67	0.01
KL22-04	369	372	0.77	7700	0.29	3.1	145	25	6	136	1	21	0.5	5.0	55	0.01
KL22-04	372	374.9	0.69	6900	0.4	2.2	58	10	0.01	198	0.01	19	0.01	6.8	60	0.01
KL22-04	374.9	378	0.51	5100	0.43	1.4	33	6	2	80	0.01	6	0.01	3.3	30	0.01
KL22-04	378	381	0.7	7000	0.49	1.5	32	8	0.01	139	0.01	10	0.01	4.9	21	0.01
KL22-04	381	384.1	0.52	5200	0.43	1.2	35	7	1	78	0.01	6	0.01	3.5	35	0.01
KL22-04	384.1	387	0.99	9900	0.6	2.9	53	10	3	73	0.01	15	0.2	4.8	70	0.01
KL22-04	387	390	0.62	6200	0.46	1.4	41	11	3	40	1	12	0.3	4.5	50	0.01
KL22-04	390	392.8	0.67	6700	0.51	1.8	42	9	2	35	1	9	0.01	5.5	23	0.01
KL22-04	392.8	394.5	1.96	19600	1.6	3.1	88	11	1	22	1	17	0.01	6.8	50	0.01
KL22-04	394.5	396	0.72	7200	1.08	1.4	54	8	2	53	2	6	0.01	4.0	23	0.01
KL22-04	396	399	1.12	11200	1.24	5.6	244	153	44	40	4	4	5.7	7.3	100	0.01
KL22-04	399	402	0.35	3500	0.14	4.5	1200	610	130	25	0.01	2	22	1.8	166	0.15
KL22-04	402	405.6	0.65	6500	0.2	18.6	7600	2000	680	16	2	3	940	2.6	114	0.68
KL22-04	405.6	408	0.85	8500	0.85	3.7	106	67	5	13	3	7	3.4	5.8	20	0.01
KL22-04	408	411	0.73	7300	0.49	6.9	1280	1070	180	16	4	4	12.3	4.0	18	0.01
KL22-04	411	414	1.07	10700	0.25	27.3	15200	8400	1280	31	18	3	890	5.1	35	1.16
KL22-04	414	418	0.77	7700	0.45	17.5	11000	6000	1080	96	3	8	500	8.3	36	0.6
KL22-04	418	420.1	0.84	8400	0.39	13.5	8600	3500	1710	30	3	3	410	6.0	21	0.64
KL22-04	420.1	423	0.6	6000	0.65	3.1	760	376	170	28	1	6	12.2	2.0	62	0.01
KL22-04	423	426.1	0.62	6200	0.64	4	350	950	170	13	2	4	3.4	5.5	210	0.01
KL22-04	426.1	429.3	1.06	10600	0.78	17.1	2580	7800	670	29	5	6	18.7	9.1	26	0.39
KL22-04	429.3	432.5	0.7906	7906	0.47	4.6	820	600	70	11	2	3	13.9	4.3	25	0.01
KL22-04	432.5	435	0.66	6600	0.31	4.8	570	420	80	9	1	2	1.9	4.3	31	0.1
KL22-04	435	438	0.58	5800	0.3	2.6	293	302	50	15	2	4	0.01	5.3	25	0.01
KL22-04	438	439.8	0.73	7300	0.25	4.1	242	90	3	58	1	7	0.6	6.0	26	0.01
KL22-04	439.8	444	0.58	5800	0.5	4.4	8000	1270	51	44	0.01	10	8.6	4.3	26	0.54
KL22-04	444	447	0.82	8200	0.85	5.8	5100	1220	310	26	3	7	2.5	6.8	16	0.28
KL22-04	447	450	0.87	8700	0.87	2.2	134	34	3	52	2	10	0.01	4.8	24	0.01
KL22-04	450	453	0.76	7600	0.67	1.9	335	65	5	89	1	9	0.01	4.0	25	0.01
KL22-04	453	456	0.84	8400	1.36	2.6	70	40	6	34	3	4	2.3	7.8	25	0.01
KL22-04	456	459	1.03	10300	2.39	3.2	188	104	33	24	5	3	9.3	7.0	21	0.01
KL22-04	459	462	0.79	7900	1.06	2	64	32	1	54	2	8	0.01	4.5	38	0.01
KL22-04	462	465.8	0.83	8300	1.74	1.3	43	11	4	30	2	5	0.01	3.5	22	0.01
KL22-04	465.8	468	0.86	8600	1.03	1.4	40	12	1	16	2	5	0.01	7.3	40	0.01
KL22-04	468	471	0.95	9500	1.12	2	30	128	0.01	10	2	6	7.4	6.3	49	0.01
KL22-04	471	474	0.95	9500	0.87	1.1	159	8	17	19	1	4	0.01	3.8	75	0.01
KL22-04	474	477	0.84	8400	0.8	1.2	28	5	0.01	58	1	6	0.01	6.3	102	0.01
KL22-04	477	480	0.52	5200	0.35	1.1	40	11	2	32	0.01	7	0.01	2.6	76	0.01
KL22-05	213.1	216.1	0.403	4030	0.34	1.7	630	62	5	259	3	8	0.01	10.3	31	0.01
KL22-05	216.1	217.6	0.328	3280	3.06	2.3	1360	51	7	130	2	10	0.01	12.0	19	0.01
KL22-05	217.6	223.7	0.97	9700	1.68	3.2	6800	46	27	374	3	26	1	15.8	61	0.01
KL22-05	223.7	226.6	0.97	9700	1.68	3.2	6800	46	27	374	3	26	1	15.8	61	0.01
KL22-05	226.6	232.75	0.193	1930	0.67	1.5	600	261	19	710	68	10	0.01	10.8	69	0.01
KL22-05	232.75	235.6	0.193	1930	0.67	1.5	600	261	19	710	68	10	0.01	10.8	69	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL22-05	235.6	241.6	0.62	6200	0.52	2.8	1220	32	16	155	1	20	0.01	9.5	70	0.01
KL22-05	241.6	244.7	0.054	540	0.06	0.01	1580	17	11	15	0.01	9	0.01	2.0	25	0.01
KL22-05	244.7	246.3	0.054	540	0.06	0.01	1580	17	11	15	0.01	9	0.01	2.0	25	0.01
KL22-05	246.3	250.7	2.07	20700	4.99	17.2	328	28	6	26	100	42	0.01	17.6	45	0.01
KL22-05	250.7	253.5	2.07	20700	4.99	17.2	328	28	6	26	100	42	0.01	17.6	45	0.01
KL22-05	253.5	255.6	2.07	20700	4.99	17.2	328	28	6	26	100	42	0.01	17.6	45	0.01
KL22-05	255.6	258.1	0.181	1810	0.11	2.3	1080	22	10	5	2	13	0.01	2.3	26	0.01
KL22-05	258.1	261.1	0.21	2100	0.22	3	4070	26	14	4	4	8	0.01	5.3	27	0.01
KL22-05	261.1	264.1	0.1	1000	0.05	1.5	2490	86	11	5	2	4	0.9	1.5	18	0.01
KL22-05	264.1	267.1	0.127	1270	0.14	3.5	11200	1190	10	4	20	9	0.8	10.6	35	0.01
KL22-05	267.1	270.1	1.44	14400	0.8	9.7	570	30	25	14	2	29	0.2	11.0	73	0.01
KL22-05	270.1	273.4	1.51	15100	0.87	2.4	260	22	10	144	0.01	18	0.7	7.5	80	0.1
KL22-05	273.4	276.1	0.57	5700	0.35	1.8	1700	26	36	610	8	14	3.8	9.0	96	0.1
KL22-05	276.1	279.1	0.98	9800	1.04	3.1	1210	18	18	107	6	32	0.01	13.1	82	0.01
KL22-05	279.1	282.1	0.81	8100	0.58	2.5	160	12	5	28	0.01	33	0.01	10.0	77	0.01
KL22-05	282.1	283.9	0.64	6400	0.36	1.2	252	20	2	18	0.01	19	0.01	6.8	58	0.01
KL22-05	283.9	285.1	3.3	33000	1.56	4.5	740	19	6	19	4	32	0.01	15.0	83	0.01
KL22-05	285.1	286.3	1.02	10200	0.64	1.4	256	26	0.01	5	1	46	0.01	7.0	76	0.01
KL22-05	286.3	286.9	6.04	60400	3.34	5.4	210	22	5	109	1	52	0.01	10.0	60	0.11
KL22-05	286.85	288.3	7.34	73400	5.62	8.9	243	23	3	148	2	90	0.01	22.0	70	0.01
KL22-05	288.3	291.6	1.65	16500	0.83	3.1	71	21	4	239	2	9	0.01	7.3	115	0.19
KL22-05	291.6	294	3.87	38700	8.89	8	60	29	0.01	182	3	22	0.01	7.0	132	0.1
KL22-05	294	296.45	7.47	74700	8.66	12.5	110	26	0.01	116	4	35	0.01	20.0	216	0.01
KL22-05	296.45	298.1	1.85	18500	3.14	3.4	56	8	1	75	4	9	0.01	7.1	314	0.1
KL22-05	298.1	299.7	0.64	6400	0.15	1.2	119	35	1	167	0.01	7	0.01	5.1	207	0.01
KL22-05	299.7	302.1	0.6	6000	0.26	1.2	31	5	0.01	130	0.01	8	0.01	6.0	146	0.01
KL22-05	302.1	304.3	1.73	17300	2.45	3.3	70	11	1	62	1	10	0.01	9.5	231	0.01
KL22-05	304.3	306.5	1.67	16700	1.95	3.5	69	10	4	28	0.01	12	0.01	9.5	182	0.1
KL22-05	306.5	308.9	1.46	14600	1.52	3.7	63	9	4	155	1	9	0.01	12.7	268	0.1
KL22-05	308.9	312	0.97	9700	1.47	3.1	50	12	1	52	2	13	0.01	10.5	197	0.01
KL22-05	312	315	1.06	10600	1.52	3.6	45	10	1	79	3	10	0.01	9.0	167	0.01
KL22-05	315	318	1.31	13100	1.63	2.9	41	11	0.01	90	1	13	0.01	8.0	183	0.01
KL22-05	318	321	0.83	8300	0.86	1.9	56	10	0.01	143	1	14	0.01	6.6	205	0.01
KL22-05	321	324	1.03	10300	1	2	54	10	2	124	1	12	0.01	9.3	171	0.01
KL22-05	324	327	1.02	10200	0.87	1.7	56	12	1	39	0.01	11	0.01	6.3	164	0.01
KL22-05	327	330	0.66	6600	0.6	1.3	63	10	0.01	29	0.01	11	0.01	4.5	139	0.01
KL22-05	330	333	0.565	5650	0.5	1.2	50	10	0.01	26	0.01	10	0.01	4.5	106	0.01
KL22-05	333	336	0.7	7000	0.52	1.3	68	16	0.01	42	0.01	15	0.01	5.5	97	0.01
KL22-05	336	339	0.65	6500	0.44	1.8	95	18	2	121	0.01	15	0.01	5.5	71	0.01
KL22-05	339	342	0.595	5950	0.51	1.1	67	17	0.01	35	0.01	13	0.01	4.0	80	0.01
KL22-05	342	345	0.69	6900	0.52	1.2	64	12	0.01	16	0.01	13	0.01	4.8	123	0.01
KL22-05	345	348	0.92	9200	0.59	3.7	830	860	76	15	2	10	2.2	8.3	100	0.21
KL22-05	348	350	0.88	8800	0.73	1.9	74	47	10	23	1	12	0.01	4.5	96	0.01
KL22-05	350	352.1	0.63	6300	0.43	4.6	100	76	140	57	1	11	1.6	3.3	82	0.1
KL22-05	352.1	354.7	0.65	6500	0.45	2	66	32	10	93	0.01	14	0.01	3.3	80	0.01
KL22-05	354.7	356.7	0.56	5600	0.37	1.2	54	17	1	36	1	12	2.1	3.0	93	0.01
KL22-05	356.7	358.7	0.65	6500	0.45	1.7	50	18	1	25	1	13	0.01	3.0	104	0.01
KL22-05	358.7	361.6	0.87	8700	0.72	1.7	60	27	3	11	0.01	13	0.01	4.8	106	0.01
KL22-05	361.6	364.6	0.56	5600	0.43	1	39	14	0.01	27	0.01	9	0.01	2.3	119	0.01
KL22-05	364.6	367.6	0.66	6600	0.64	1.7	89	40	3	97	0.01	21	1.1	4.0	114	0.01
KL22-05	367.6	370.6	1.47	14700	0.63	18.4	1160	23500	650	38	0.01	14	26	7.8	75	0.15
KL22-05	370.6	373.6	0.7	7000	0.62	1.6	66	8	4	56	0.01	18	0.01	4.1	113	0.01
KL22-05	373.6	376.6	0.89	8900	0.38	4.9	296	131	35	64	0.01	15	0.4	3.8	81	0.01
KL22-05	376.6	379.6	0.69	6900	0.35	2.5	174	58	6	61	0.01	15	0.01	2.9	78	0.01
KL22-05	379.6	382.6	1.01	10100	1.02	3.7	105	83	14	106	0.01	13	0.2	5.3	113	0.01
KL22-05	382.6	385.6	1.08	10800	0.8	18.7	4600	32100	900	47	0.01	11	47	22.5	118	0.43
KL22-05	385.6	388.6	1.1	11000	0.54	7.4	410	221	39	304	0.01	13	0.5	4.5	72	0.01
KL22-05	388.6	391.6	1.1	11000	0.8	8.4	580	255	110	82	1	11	1.7	3.3	66	0.01
KL22-05	391.6	394.6	1.67	16700	0.68	10.5	740	4700	540	79	0.01	15	15.7	4.0	70	0.2
KL22-05	394.6	397.6	0.65	6500	0.42	3.8	174	105	180	57	1	14	2.1	5.5	75	0.16
KL22-05	397.6	400.6	1.02	10200	0.57	10.9	740	343	220	67	0.01	14	10.3	7.5	125	0.01
KL22-05	400.6	403.6	0.71	7100	0.31	1.8	119	47	8	232	0.01	17	0.01	13.3	102	0.01
KL22-05	403.6	406.6	1.08	10800	0.64	3.3	163	45	5	127	0.01	19	0.01	10.5	91	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL22-05	406.6	409.75	1.54	15400	1.4	3.8	105	36	12	184	2	17	0.6	9.3	134	0.01
KL22-05	409.75	412	1.12	11200	0.44	7.9	1480	600	450	13	1	6	7.8	6.4	271	0.01
KL22-05	412	415	1.02	10200	0.21	18.5	3200	1560	2050	14	0.01	5	66	5.8	296	0.59
KL22-05	415	418	0.76	7600	0.15	9.7	1370	510	1670	17	1	7	90	3.5	201	0.61
KL22-05	418	421	1.04	10400	0.28	14.6	24300	4900	2900	19	10	7	40	5.8	188	3.07
KL22-05	421	424	0.78	7800	0.42	4.2	409	221	210	80	1	8	1.6	4.5	131	0.01
KL22-05	424	427	0.78	7800	0.52	2.7	175	72	28	28	0.01	13	0.9	5.5	140	0.01
KL22-05	427	430	0.86	8600	0.83	1.9	70	22	20	29	0.01	9	0.5	5.3	240	0.01
KL22-05	430	433	1.27	12700	1.05	2.2	46	15	5	21	0.01	11	0.7	5.5	215	0.1
KL22-05	433	436	0.68	6800	0.57	2.1	43	18	4	18	0.01	7	0.01	4.3	235	0.01
KL22-05	436	439	0.78	7800	0.67	1.9	37	14	3	13	0.01	9	0.01	3.5	265	0.01
KL22-05	439	442	0.7	7000	0.42	3	40	23	9	26	0.01	10	0.01	3.5	196	0.01
KL22-05	442	445	0.63	6300	0.19	2.8	360	127	62	15	0.01	9	0.8	4.4	205	0.01
KL22-05	445	448	0.66	6600	0.34	1.9	66	24	9	28	0.01	9	1.6	4.0	276	0.01
KL22-05	448	451	0.412	4120	0.28	1	54	23	3	27	0.01	10	0.01	4.0	193	0.01
KL22-05	451	454	0.45	4500	0.26	1.2	177	90	4	25	0.01	10	0.5	4.5	149	0.01
KL22-05	454	457	0.466	4660	0.36	1.3	95	18	1	22	0.01	8	0.01	3.8	115	0.01
KL22-05	457	460	0.63	6300	0.5	1.4	34	21	3	25	0.01	10	0.3	5.3	135	0.01
KL22-05	460	463	0.755	7550	0.76	1.7	28	10	4	26	0.01	8	0.01	6.5	70	0.01
KL22-05	463	466	0.54	5400	0.31	1.6	58	9	23	46	0.01	12	0.01	7.3	140	0.01
KL22-05	466	469	0.69	6900	0.39	3.3	379	85	170	71	0.01	13	10.9	4.8	35	0.01
KL22-05	469	472	0.85	8500	0.6	1.7	62	14	7	79	0.01	9	0.01	6.0	81	0.01
KL22-05	472	475.4	0.77	7700	0.43	1.5	40	6	1	30	0.01	0.01	0.01	4.0	72	0.01
KL22-05	475.4	478.5	0.97	9700	0.53	2	46	5	3	51	0.01	8	0.01	5.0	83	0.01
KL22-05	478.5	480.1	1.07	10700	0.45	1.9	60	22	6	44	0.01	12	0.01	5.8	74	0.01
KL22-05	480.1	483.8	1	10000	0.57	3	74	23	6	36	0.01	10	0.3	6.0	80	0.01
KL22-05	483.8	487.1	1.04	10400	0.59	3	86	16	5	41	0.01	13	1	7.0	109	0.01
KL22-05	487.1	490.6	0.78	7800	0.45	2.4	74	13	2	45	0.01	13	0.01	5.3	181	0.01
KL22-05	490.6	499.4	1.28	12800	0.83	2.3	45	14	2	53	0.01	14	0.01	5.5	107	0.01
KL22-05	499.4	502.6	1.44	14400	0.65	3.7	87	12	4	140	0.01	20	1.2	5.8	97	0.01
KL22-05	502.6	505.1	0.91	9100	0.48	2.9	56	13	2	89	0.01	14	0.01	5.5	89	0.01
KL22-05	505.1	508.6	1.4	14000	0.84	2.5	52	17	2	60	0.01	16	0.01	4.5	80	0.01
KL22-05	508.6	511.6	1.08	10800	0.54	2.3	49	13	2	111	0.01	12	0.6	5.9	94	0.01
KL22-05	511.6	514.6	0.93	9300	0.38	2.4	58	14	2	80	0.01	10	0.01	6.0	76	0.01
KL22-05	514.6	517.6	0.52	5200	0.27	1.7	55	12	2	281	0.01	11	0.01	4.0	77	0.01
KL22-05	517.6	520.1	0.62	6200	0.28	1.9	55	11	3	76	0.01	11	0.01	5.3	89	0.01
KL22-05	520.1	523.6	0.481	4810	0.25	2	58	12	3	60	1	9	0.01	4.3	76	0.01
KL22-05	523.6	526.6	0.66	6600	0.39	1.8	56	12	4	106	1	10	0.01	6.0	62	0.01
KL22-05	526.6	529.6	1.01	10100	0.44	2.7	94	61	4	120	1	15	0.6	7.5	185	0.01
KL22-05	529.6	532.6	0.89	8900	0.44	2.4	80	29	7	102	1	14	0.4	7.0	91	0.01
KL22-05	532.6	535.6	0.86	8600	0.35	5.2	910	399	580	145	1	11	24	4.7	61	0.24
KL22-05	535.6	539.7	1.09	10900	0.57	2.3	81	60	17	117	0.01	12	1.2	5.6	150	0.01
KL22-05	539.7	542.2	0.442	4420	0.17	1.3	137	42	27	240	1	14	0.4	3.8	153	0.01
KL22-05	542.2	544.8	0.394	3940	0.2	1.4	58	42	8	90	0.01	13	0.3	2.3	175	0.01
KL22-05	544.8	547.5	0.86	8600	0.42	2.4	50	28	6	135	0.01	11	0.01	5.5	220	0.01
KL22-05	547.5	550.3	0.95	9500	0.42	2.2	84	51	8	113	0.01	9	0.4	5.0	202	0.01
KL22-05	550.3	553.5	1	10000	0.39	2.5	112	86	28	150	0.01	12	1	6.0	205	0.01
KL22-05	553.5	556.6	0.86	8600	0.42	2	51	36	3	117	0.01	11	0.01	7.3	232	0.01
KL22-05	556.6	559.6	0.96	9600	0.4	2.4	68	61	34	268	0.01	16	0.9	5.0	221	0.01
KL22-05	559.6	562.4	0.99	9900	0.25	2.6	239	120	67	203	0.01	13	2.3	5.5	85	0.01
KL22-05	562.4	565.6	1.03	10300	0.53	2.3	58	42	12	209	0.01	13	1.2	7.0	81	0.01
KL22-05	565.6	568.2	4.18	41800	1.37	10.7	230	30	8	700	0.01	46	0.7	10.0	95	0.01
KL22-05	568.2	573.1	3.44	34400	1.75	9.2	276	43	17	151	0.01	42	0.2	13.0	48	0.01
KL22-05	573.1	575.6	7.21	72100	4.4	12.5	394	34	22	157	0.01	105	0.01	8.0	23	0.01
KL22-05	575.6	578.5	2.7	27000	1.64	5.7	302	30	13	168	0.01	83	0.01	12.0	28	0.01
KL22-05	578.5	580.6	4.17	41700	2.99	9.4	254	20	41	26	0.01	73	0.01	8.0	32	0.1
KL22-05	580.6	583.3	2.06	20600	1.64	4.1	154	20	42	51	0.01	36	0.01	7.5	28	0.01
KL22-05	583.3	586.3	0.57	5700	0.68	0.9	139	26	10	90	1	43	0.01	4.2	31	0.01
KL22-05	586.3	589	1.35	13500	1.04	3.7	201	24	3	34	1	69	0.01	4.2	43	0.01
KL22-05	589	591.2	1.13	11300	1.32	1.8	149	24	15	0.01	1	46	0.3	9.0	40	0.01
KL22-05	591.2	593.4	2.1	21000	1.94	4.5	256	26	26	4	1	63	1.3	17.0	47	0.01
KL22-05	593.4	595.5	2.15	21500	2.04	4.8	420	24	5	0.01	0.01	94	0.5	13.5	47	0.01
KL22-05	595.5	597.9	4.34	43400	2.86	11.6	960	25	0.01	0.01	0.01	130	0.2	13.5	45	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL22-05	597.9	601.6	2.28	22800	2.4	5.5	1040	24	1	0.01	0.01	118	0.3	20.0	35	0.01
KL22-05	601.6	604.6	2.52	25200	2.44	6.1	900	22	1	0.01	0.01	142	0.3	26.0	20	0.01
KL22-05	604.6	607.6	2.33	23300	2.06	7	1280	26	2	0.01	0.01	59	0.01	4.5	38	0.01
KL22-05	607.6	611.55	2.55	25500	2.02	6.9	890	25	2	0.01	0.01	76	0.9	23.0	24	0.01
KL22-05	611.55	613.6	2.03	20300	1.28	5	430	21	3	0.01	0.01	56	0.01	14.0	26	0.01
KL22-05	613.6	616.6	1.46	14600	1.75	3.8	340	20	6	0.01	1	51	0.01	14.2	18	0.01
KL22-05	616.6	619.6	1.52	15200	1.29	3.5	338	18	3	0.01	0.01	60	0.01	14.7	12	0.01
KL22-05	619.6	622.45	2.96	29600	3.32	9.7	730	20	2	18	3	64	0.3	18.0	24	0.01
KL22-05	622.45	624.5	3.06	30600	2.45	12.1	1860	21	7	8	2	39	0.01	18.0	28	0.01
KL22-05	624.5	628.6	0.438	4380	0.78	3.7	3370	16	6	3	8	20	0.5	6.2	28	0.01
KL22-05	628.6	631.6	0.297	2970	0.13	1.7	285	18	7	2	2	7	0.01	2.6	12	0.01
KL22-05	631.6	634.6	0.088	880	0.07	0.7	180	18	9	15	2	7	0.6	1.2	17	0.01
KL22-05	634.6	637.6	0.437	4370	0.47	1.9	440	42	9	0.01	3	10	0.4	6.2	18	0.01
KL22-05	637.6	640.6	0.21	2100	0.36	2.3	311	12	14	0.01	1	6	0.2	1.0	23	0.01
KL22-05	640.6	643.6	0.086	860	0.09	0.01	115	24	4	0.01	3	3	0.01	2.0	10	0.01
KL22-05	643.6	646.6	0.0198	198	0.01	0.01	156	19	4	0.01	0.01	3	0.01	0.5	14	0.01
KL22-05	646.6	649.6	0.036	360	0.01	0.01	102	16	3	16	0.01	4	0.01	1.0	13	0.01
KL22-05	649.6	652.6	0.063	630	0.05	0.01	126	19	5	17	1	3	0.3	1.5	21	0.01
KL22-05	652.6	654.7	0.23	2300	0.18	1.5	219	15	9	11	1	8	0.01	3.1	18	0.01
KL22-05	654.7	658.6	0.339	3390	0.2	1.8	210	12	9	13	0.01	12	0.01	4.2	20	0.01
KL22-05	658.6	662	0.68	6800	0.36	3.7	375	13	5	13	1	17	0.01	7.0	37	0.01
KL22-05	662	664.4	0.384	3840	0.21	1.6	256	10	8	10	2	11	0.4	5.2	34	0.01
KL22-05	664.4	667.5	0.089	890	0.17	0.8	198	15	5	12	3	6	0.2	2.2	22	0.01
KL22-05	667.5	670.4	0.152	1520	0.09	1.8	247	13	5	0.01	0.01	7	0.01	1.0	20	0.01
KL22-05	670.4	673.6	0.0345	345	0.01	0.01	150	17	3	6	0.01	6	0.01	1.5	20	0.01
KL22-05	673.6	676.6	0.289	2890	0.13	1.8	225	17	3	10	1	7	0.01	4.5	15	0.01
KL22-05	676.6	679.6	0.268	2680	0.12	2.3	251	16	4	6	2	7	0.01	3.5	16	0.01
KL22-05	679.6	682.6	0.048	480	0.02	0.01	135	17	3	8	0.01	4	0.4	0.7	11	0.01
KL22-05	682.6	685.6	0.065	650	0.02	0.01	138	20	4	10	0.01	5	2.2	1.2	12	0.01
KL22-05	685.6	688.6	0.0223	223	0.01	0.01	120	16	2	0.01	0.01	4	0.01	0.0	11	0.01
KL22-05	688.6	691.6	0.048	480	0.02	0.6	111	21	3	12	2	3	0.01	0.5	10	0.01
KL22-05	691.6	694.6	0.046	460	0.01	0.01	118	17	2	3	1	3	0.01	0.0	8	0.01
KL22-05	694.6	697.6	0.066	660	0.02	0.5	222	20	4	11	2	4	0.01	0.9	13	0.01
KL22-05	697.6	699.25	0.187	1870	0.06	1.6	246	26	4	5	4	4	0.01	3.0	14	0.01
KL22-05	699.25	703.85	0.265	2650	0.11	2.9	380	22	8	14	4	5	0.01	6.7	30	0.01
KL22-05	703.85	706.6	0.116	1160	0.03	1	159	18	6	8	1	6	0.01	2.7	15	0.01
KL22-05	706.6	709.6	0.086	860	0.03	1	228	21	4	10	1	3	0.01	0.0	15	0.01
KL22-05	709.6	712.6	0.0098	98	0.11	3	1300	1090	26	23	3	2	1.3	2.0	12	0.01
KL22-05	712.6	715.6	0.12	1200	0.07	1.3	276	36	4	4	0.01	4	0.01	2.0	16	0.01
KL22-05	715.6	718.6	0.286	2860	0.13	2.4	317	20	7	44	0.01	7	0.01	8.0	18	0.01
KL22-05	718.6	721.15	0.498	4980	0.25	4.1	800	22	5	6	0.01	17	0.01	6.3	27	0.01
KL22-05	721.15	724.6	1.06	10600	0.86	3.5	344	93	3	16	0.01	19	0.01	4.0	17	0.01
KL22-05	724.6	727.6	0.439	4390	0.3	1.3	132	117	0.01	10	0.01	8	0.01	1.0	13	0.01
KL22-05	727.6	730.6	0.78	7800	0.38	2.5	107	20	4	63	0.01	14	0.01	3.7	21	0.01
KL22-05	730.6	733.6	0.21	2100	0.07	0.01	17	11	1	50	0.01	3	0.01	1.2	38	0.01
KL22-05	733.6	736.6	0.435	4350	0.05	0.8	23	12	1	49	0.01	6	0.01	3.5	16	0.01
KL22-05	736.6	741.5	1.01	10100	0.14	4.8	53	18	1	41	0.01	9	0.01	4.7	15	0.01
KL22-05	741.5	745.6	0.91	9100	0.4	3.7	394	23	4	6	0.01	22	0.01	7.4	32	0.01
KL22-05	745.6	748.6	1.43	14300	1.04	7.5	1900	43	1	6	0.01	38	0.01	8.1	42	0.01
KL22-05	748.6	751.6	0.223	2230	0.12	1.1	164	14	1	11	0.01	6	0.01	3.7	26	0.01
KL22-05	751.6	754.6	0.6	6000	0.4	2	276	13	3	5	1	20	0.01	7.7	29	0.01
KL22-05	754.6	757.6	0.96	9600	0.39	2.5	374	21	0.01	6	0.01	32	0.01	11.0	35	0.01
KL22-05	757.6	760.6	0.94	9400	0.39	4.5	750	13	1	6	0.01	17	0.01	5.7	31	0.01
KL22-05	760.6	763.6	0.93	9300	0.48	3.4	126	9	1	16	0.01	14	0.01	4.7	33	0.01
KL22-05	763.6	766.6	0.486	4860	0.21	2	116	10	1	12	0.01	11	0.01	4.0	40	0.01
KL22-05	766.6	769.6	0.65	6500	0.33	2.6	170	11	3	12	0.01	14	0.3	7.3	38	0.01
KL22-05	769.6	772.6	0.359	3590	0.21	1.2	62	8	1	9	0.01	12	0.01	2.7	35	0.01
KL22-05	772.6	775.2	0.6	6000	0.33	2	75	10	2	31	0.01	14	0.01	3.5	26	0.01
KL22-05	775.2	778.75	0.183	1830	0.07	1.6	24	10	2	30	0.01	6	0.01	2.7	26	0.01
KL22-05	778.75	780.7	0.113	1130	0.01	0.01	19	9	3	190	0.01	6	0.01	0.7	44	0.01
KL22-05	780.7	783.2	0.69	6900	0.35	4	730	11	5	4	0.01	16	0.01	4.7	52	0.01
KL22-05	783.2	785.65	0.299	2990	0.2	1.4	125	11	6	26	0.01	11	0.01	1.2	31	0.01
KL22-05	785.65	787.6	0.7	7000	0.21	1.6	47	18	2	144	0.01	12	0.6	4.4	65	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL22-05	787.6	790.6	0.269	2690	0.19	1	35	9	0.01	71	0.01	6	0.01	1.7	15	0.01
KL22-05	790.6	793.6	0.339	3390	0.26	1.1	44	10	3	64	0.01	6	1	1.5	115	0.01
KL22-05	793.6	797.4	0.321	3210	0.14	4.6	950	530	82	145	3	5	46	1.5	153	0.1
KL22-05	797.4	799.6	0.792	7920	0.51	4.6	286	137	70	1950	3	13	18.3	5.0	61	0.1
KL22-05	799.6	802.6	0.494	4940	0.2	1.4	68	18	4	278	0.01	9	0.5	3.5	46	0.01
KL22-05	802.6	804.45	0.925	9250	0.32	1.8	64	11	2	850	0.01	8	0.01	4.2	59	0.01
KL22-05	804.45	808.6	0.28	2800	0.09	1.2	35	12	1	189	0.01	5	1.2	0.5	42	0.01
KL22-05	808.6	811.6	0.373	3730	0.16	1.1	36	9	1	172	0.01	7	0.3	1.7	36	0.01
KL22-05	811.6	814.6	0.21	2100	0.09	0.8	28	8	1	131	0.01	3	0.4	0.0	15	0.01
KL22-05	814.6	817.6	0.53	5300	0.19	1.3	61	32	1	189	0.01	9	0.6	3.0	16	0.01
KL22-05	817.6	820.6	1.2	12000	0.21	2.1	73	11	1	72	0.01	18	0.3	3.0	15	0.01
KL22-05	820.6	823.6	0.477	4770	0.13	1	41	6	1	47	0.01	6	0.4	4.2	16	0.01
KL22-05	823.6	826.1	0.82	8200	0.36	1.6	66	9	4	9	0.01	14	0.4	7.3	23	0.01
KL22-05	826.1	829.6	2.08	20800	0.6	2	181	13	3	5	0.01	27	0.2	7.0	55	0.01
KL22-05	829.6	832.6	1.73	17300	0.51	5.7	307	15	1	10	0.01	31	0.3	12.0	51	0.01
KL22-05	832.6	837.05	1.03	10300	0.36	4.9	710	14	3	22	0.01	19	0.4	10.5	31	0.01
KL22-05	837.05	841.6	0.155	1550	0.05	0.9	165	13	3	8	0.01	2	0.3	2.0	28	0.01
KL22-05	841.6	844.6	1.04	10400	0.31	4.8	730	13	2	65	0.01	13	0.2	7.5	25	0.01
KL22-05	844.6	847.6	0.767	7670	0.29	5.5	750	14	1	40	0.01	10	0.01	11.3	27	0.01
KL22-05	847.6	850.6	1.08	10800	0.33	4.6	930	12	3	13	0.01	14	0.01	10.7	32	0.01
KL22-05	850.6	853.6	0.76	7600	0.2	3.8	1000	10	2	3	0.01	14	0.2	8.0	56	0.01
KL22-05	853.6	856.6	0.52	5200	0.18	3.8	700	24	4	4	0.01	12	0.01	6.7	39	0.01
KL22-05	856.6	859.6	0.99	9900	0.31	5.1	890	11	1	39	0.01	19	0.2	7.0	36	0.01
KL22-05	859.6	862.6	0.705	7050	0.36	3.1	420	9	3	13	0.01	16	0.01	7.0	22	0.01
KL22-05	862.6	865.6	1.7	17000	0.43	5.1	388	9	3	74	0.01	20	0.01	8.0	32	0.01
KL22-05	865.6	868.6	0.23	2300	0.1	0.7	224	14	2	14	0.01	4	0.01	3.2	36	0.01
KL22-05	868.6	871.6	0.497	4970	0.11	2.2	460	11	2	6	0.01	7	0.01	5.4	38	0.01
KL22-06	221.9	225.1	0.36	3600	0.41	1.4	106	35	11	1150	0.01	11	0.5	11.0	20	0.01
KL22-06	225.1	232.6	1.12	11200	1.87	3.9	760	60	100	1375	4	17	2	16.0	22	0.2
KL22-06	232.6	233.4	1.95	19500	1.7	3.5	288	30	10	1860	1	25	0.5	17.0	30	0.01
KL22-06	233.4	235.6	1.95	19500	1.7	3.5	288	30	10	1860	1	25	0.5	17.0	30	0.01
KL22-06	235.6	238.6	1.95	19500	1.7	3.5	288	30	10	1860	1	25	0.5	17.0	30	0.01
KL22-06	238.6	240.85	1.9	19000	2.12	8.7	3800	25	11	100	2	40	0.01	12.0	17	0.01
KL22-06	240.85	241.6	1.9	19000	2.12	8.7	3800	25	11	100	2	40	0.01	12.0	17	0.01
KL22-06	241.6	245	0.995	9950	0.9	4.2	3400	40	4	41	1	50	0.3	17.3	23	0.01
KL22-06	245	250.6	0.995	9950	0.9	4.2	3400	40	4	41	1	50	0.3	17.3	23	0.01
KL22-06	250.6	254.6	0.877	8770	0.58	2.3	760	21	2	10	0.01	43	0.2	10.3	25	0.01
KL22-06	254.6	257.65	0.877	8770	0.58	2.3	760	21	2	10	0.01	43	0.2	10.3	25	0.01
KL22-06	257.65	259.6	0.289	2890	0.2	3.1	3200	16	7	2	0.01	12	0.2	8.9	19	0.01
KL22-06	259.6	262.15	0.289	2890	0.2	3.1	3200	16	7	2	0.01	12	0.2	8.9	19	0.01
KL22-06	262.15	264.3	0.578	5780	0.56	5.2	3200	19	9	28	0.01	21	0.01	12.3	39	0.01
KL22-06	264.3	268.3	1.36	13600	1.2	3	2700	14	3	5	4	54	0.3	14.0	15	0.01
KL22-06	268.3	271.6	1.46	14600	1.33	7.1	1140	17	7	15	0.01	41	0.01	12.0	31	0.01
KL22-06	271.6	273.6	1.46	14600	1.33	7.1	1140	17	7	15	0.01	41	0.01	12.0	31	0.01
KL22-06	273.6	275.4	2.08	20800	2.52	11.8	780	16	0.01	53	1	76	0.01	17.0	19	0.01
KL22-06	275.4	278.5	0.54	5400	0.51	3.9	710	15	3	30	0.01	32	0.01	6.3	18	0.01
KL22-06	278.5	280.6	0.55	5500	0.44	1.4	241	16	3	42	0.01	33	0.01	7.0	34	0.01
KL22-06	280.6	283.9	0.59	5900	0.55	1.2	211	15	0.01	82	0.01	43	0.01	5.8	22	0.01
KL22-06	283.9	285.9	2.28	22800	1.7	4.2	212	13	0.01	250	0.01	71	0.01	19.0	26	0.01
KL22-06	285.9	289.25	1.38	13800	1.22	2	124	12	0.01	510	1	55	0.01	11.5	36	0.01
KL22-06	289.25	292.8	3.09	30900	2.15	4.5	67	13	1	26	2	29	0.01	22.0	146	0.01
KL22-06	292.8	294.6	0.46	4600	0.3	1.2	51	18	3	74	0.01	6	0.01	3.5	98	0.01
KL22-06	294.6	297.6	1.29	12900	1.25	2.1	37	23	2	34	0.01	13	0.01	9.5	115	0.01
KL22-06	297.1	297.6	1.5	15000	1.4	3.9	1140	22	2	39	2	51	0.3	16.5	51	0.01
KL22-06	297.6	300.1	1.52	15200	1.41	2.5	95	46	1	14	0.01	7	0.3	11.3	185	0.01
KL22-06	300.1	303.1	1.41	14100	1.31	2.4	64	10	0.01	25	1	5	0.2	7.0	74	0.01
KL22-06	303.1	306.1	0.84	8400	0.73	1.7	49	16	1	21	1	7	0.2	6.0	135	0.01
KL22-06	306.1	309.1	1.01	10100	1.02	2.2	42	12	0.01	23	3	9	0.01	5.9	125	0.01
KL22-06	309.1	312.1	1.19	11900	1.3	2.3	132	30	1	21	2	14	0.01	12.8	106	0.01
KL22-06	312.1	315.1	0.77	7700	0.56	1.3	45	13	0.01	35	1	13	0.01	4.5	106	0.01
KL22-06	315.1	318.1	0.76	7600	0.59	1.8	44	11	1	33	1	9	0.01	6.8	101	0.01
KL22-06	318.1	321.1	0.92	9200	0.84	1.6	45	12	2	113	1	13	0.01	5.8	54	0.01
KL22-06	321.1	324.1	0.963	9630	1.33	2.2	44	12	2	70	2	11	0.01	7.3	80	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL22-06	324.1	327.1	1.1	11000	1.19	1.9	80	16	2	29	0.01	10	0.01	10.3	65	0.01
KL22-06	327.1	330.1	0.87	8700	0.97	1.3	44	10	1	13	0.01	8	0.01	7.8	97	0.01
KL22-06	330.1	333.1	0.952	9520	1.12	2.1	54	12	4	50	2	10	0.01	6.0	79	0.01
KL22-06	333.1	336.1	0.974	9740	0.47	2	36	12	5	38	1	8	0.01	8.3	70	0.01
KL22-06	336.1	339.6	1.38	13800	0.87	2.5	39	36	7	37	1	12	1.1	7.5	65	0.01
KL22-06	339.6	342.7	1.09	10900	0.63	3.4	78	70	320	86	20	12	3.5	7.5	68	0.14
KL22-06	342.7	345.6	1.14	11400	0.46	7	256	121	2600	59	46	7	8.2	11.0	76	0.26
KL22-06	345.6	348.1	0.87	8700	0.49	4.5	329	184	1100	67	52	11	11.5	8.5	68	0.34
KL22-06	348.1	351.1	0.67	6700	0.46	4.1	710	386	620	50	8	10	8.1	7.0	42	0.39
KL22-06	351.1	354.1	1.07	10700	1.47	2.3	36	18	23	36	0.01	8	0.2	10.3	59	0.01
KL22-06	354.1	357.1	0.84	8400	1.06	1.2	47	30	4	33	1	8	0.2	7.3	82	0.01
KL22-06	357.1	360.6	0.75	7500	0.74	1	35	15	10	72	1	10	0.01	6.5	65	0.01
KL22-06	360.6	363.4	0.63	6300	0.44	0.9	37	16	6	52	0.01	11	0.01	4.5	66	0.01
KL22-06	363.4	365.9	0.83	8300	0.66	1.7	45	23	7	40	1	13	0.01	6.1	73	0.01
KL22-06	365.9	368.1	0.78	7800	0.58	0.9	42	10	5	34	1	13	0.01	3.8	66	0.01
KL22-06	368.1	371.1	0.53	5300	0.34	0.9	55	16	3	26	1	14	0.01	3.5	78	0.01
KL22-06	371.1	375.8	0.74	7400	0.53	1.1	40	21	4	41	2	12	0.01	4.8	75	0.01
KL22-06	375.8	378.1	0.5	5000	0.4	0.9	42	15	10	71	1	12	0.2	3.0	68	0.01
KL22-06	378.1	380.8	0.74	7400	0.49	1.2	53	31	10	710	1	25	0.3	5.9	68	0.01
KL22-06	380.8	382.6	0.68	6800	0.59	1	56	16	8	975	0.01	14	0.01	7.8	85	0.01
KL22-06	382.6	385.6	0.65	6500	0.46	1.3	52	16	240	640	1	10	5.1	5.8	62	0.01
KL22-06	385.6	387.1	0.87	8700	0.62	1.7	42	19	42	75	0.01	12	1.4	11.8	65	0.01
KL22-06	387.1	389	0.78	7800	0.52	1.8	199	172	1580	115	2	10	23	11.0	29	0.15
KL22-06	389	391.6	0.78	7800	0.9	1.9	58	19	660	145	0.01	12	4	8.5	46	0.16
KL22-06	391.6	394.6	0.78	7800	0.51	1.2	52	11	8	435	0.01	11	0.01	4.8	83	0.01
KL22-06	394.6	397.6	0.74	7400	0.78	1.5	55	18	59	73	0.01	11	0.01	4.5	75	0.44
KL22-06	397.6	400.8	0.89	8900	0.78	1.3	48	9	37	314	0.01	15	0.01	7.6	131	0.33
KL22-06	400.8	403.4	0.877	8770	0.55	1	46	7	3	343	0.01	14	0.01	5.3	98	0.01
KL22-06	403.4	406.6	0.82	8200	0.54	1.2	46	10	4	138	0.01	14	0.01	3.8	103	0.1
KL22-06	406.6	409.6	1.4	14000	0.6	1.8	73	9	3	129	0.01	18	0.01	2.5	91	0.01
KL22-06	409.6	412.6	1.68	16800	0.67	2.3	96	20	4	480	0.01	17	0.01	2.5	87	0.01
KL22-06	412.6	415.6	1.41	14100	0.68	1.6	70	10	4	73	1	18	0.01	8.5	91	0.01
KL22-06	415.6	418.6	1.43	14300	0.55	1.4	76	10	3	460	0.01	14	0.01	3.5	73	0.01
KL22-06	418.6	421.6	1.15	11500	0.49	1.2	81	13	3	715	0.01	13	0.01	3.5	72	0.01
KL22-06	421.6	424.6	0.68	6800	0.48	0.9	46	10	4	565	0.01	12	0.01	5.0	87	0.01
KL22-06	424.6	426.55	0.61	6100	0.3	0.9	42	10	3	360	0.01	11	0.01	3.5	86	0.01
KL22-06	426.55	430.6	0.55	5500	0.22	0.9	50	16	38	850	0.01	12	0.3	4.3	91	0.01
KL22-06	430.6	433.6	0.36	3600	0.12	0.01	50	16	6	1260	0.01	11	0.01	4.3	82	0.01
KL22-06	433.6	437.75	0.75	7500	2.38	2	118	28	17	860	0.01	12	0.2	7.5	73	0.01
KL22-06	437.75	441.3	0.33	3300	0.28	0.6	48	14	5	246	0.01	9	0.01	2.5	76	0.01
KL22-06	441.3	445.05	0.62	6200	0.43	1.3	60	18	5	610	0.01	12	0.01	5.3	100	0.01
KL22-06	445.05	447.35	1.68	16800	0.97	3.7	168	12	7	146	0.01	40	0.01	18.5	62	0.01
KL22-06	447.35	451.4	2.65	26500	1.46	7	165	16	15	48	0.01	56	0.4	26.5	80	0.01
KL22-06	451.4	454.6	3.03	30300	3.13	12.8	231	14	8	78	1	36	0.01	12.0	72	0.01
KL22-06	454.6	456.9	0.23	2300	0.22	0.8	48	18	20	35	0.01	10	0.01	7.5	55	0.01
KL22-06	456.9	458.9	0.142	1420	0.13	0.01	30	14	11	32	2	5	0.01	6.8	73	0.01
KL22-06	458.9	460.6	0.113	1130	0.11	0.01	27	16	5	795	2	4	0.01	6.8	87	0.01
KL22-06	460.6	463.6	0.43	4300	0.45	0.9	78	19	9	44	1	11	0.01	10.0	141	0.01
KL22-06	463.6	466.6	0.52	5200	0.72	1.7	79	18	22	12	2	26	0.01	10.8	100	0.01
KL22-06	466.6	469.6	0.68	6800	0.79	1.8	86	23	27	30	2	36	0.01	9.3	79	0.01
KL22-06	469.6	472.6	0.86	8600	0.43	1.4	78	14	24	78	0.01	41	0.01	9.8	62	0.01
KL22-06	472.6	475.6	1.41	14100	1.28	3.9	104	12	13	15	0.01	89	0.01	15.5	76	0.01
KL22-06	475.6	478.6	0.6	6000	0.43	1.4	240	23	28	106	0.01	78	0.01	9.3	90	0.01
KL22-06	478.6	481.6	0.28	2800	0.29	0.7	87	14	39	34	0.01	71	0.01	3.3	112	0.01
KL22-06	481.6	484.6	0.66	6600	1.3	2.7	164	20	40	201	0.01	71	0.01	6.2	73	0.01
KL22-06	484.6	487.6	0.81	8100	1.26	3	164	20	90	81	0.01	50	0.4	13.5	78	0.01
KL22-06	487.6	490.6	0.145	1450	0.26	0.01	45	10	21	235	0.01	18	0.01	2.8	73	0.01
KL22-06	490.6	493.6	0.37	3700	0.6	0.7	60	9	27	90	0.01	11	0.01	5.8	86	0.01
KL22-06	493.6	496.6	0.3	3000	0.57	1.1	53	10	37	100	0.01	5	0.01	3.0	79	0.01
KL22-06	496.6	499.6	1.8	18000	1.15	2	134	10	29	61	0.01	14	0.01	3.5	65	0.01
KL22-06	499.6	502.6	0.38	3800	0.36	0.01	63	9	26	36	0.01	4	0.01	4.5	85	0.01
KL22-06	502.6	505.6	0.21	2100	0.42	1	45	10	26	19	0.01	5	0.01	5.0	62	0.01
KL22-06	505.6	508.6	0.15	1500	0.26	0.01	27	9	22	30	0.01	3	0.01	2.0	100	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL22-06	508.6	511.6	0.172	1720	0.22	0.01	43	14	34	34	0.01	4	0.01	2.5	72	0.01
KL22-06	511.6	514.6	0.0332	332	0.03	0.01	27	16	21	43	0.01	3	0.01	1.1	43	0.01
KL22-06	514.6	517.6	0.063	630	0.13	0.01	27	14	10	260	1	3	0.01	1.6	62	0.01
KL22-06	517.6	520.6	0.092	920	0.23	0.01	32	15	5	209	1	4	0.01	1.5	64	0.01
KL22-06	520.6	523.6	0.084	840	0.24	0.01	28	13	11	700	0.01	3	0.01	2.5	57	0.01
KL22-06	523.6	526.6	0.041	410	0.15	0.01	26	14	13	1250	0.01	2	0.01	2.0	48	0.01
KL22-06	526.6	529.6	0.0165	165	0.04	0.01	24	17	35	900	0.01	3	0.01	1.0	66	0.01
KL22-06	529.6	532.6	0.053	530	0.86	0.8	49	30	39	74	0.01	2	0.01	1.8	50	0.01
KL22-06	532.6	535.6	1.82	18200	2.1	5.8	191	15	52	230	2	11	0.01	23.5	50	0.01
KL22-06	535.6	538	0.94	9400	0.59	3.1	131	14	18	38	1	10	0.01	8.5	38	0.01
KL22-06	538	541.6	5.36	53600	2.45	27.2	1710	46	180	66	10	58	0.4	17.0	41	0.1
KL22-06	541.6	544.6	2.08	20800	0.88	6	234	68	420	38	3	16	3.5	20.5	53	0.01
KL22-06	544.6	547.6	1.61	16100	0.48	4.9	1010	269	2400	30	3	11	5.6	16.0	36	0.01
KL22-06	547.6	549	3.1	31000	0.62	4.3	2100	810	450	38	3	16	6.3	43.5	88	0.01
KL22-06	549	552.3	0.04	400	0.02	0.01	950	780	16	6	1	2	0.01	3.3	14	0.01
KL22-07	0	4	0.0016	16	0.03	0.01	280	35	7	0.01	0.01	0.01	0.7	1.3	20	0.01
KL22-07	4	6.1	0.005	50	0.15	0.01	126	29	8	0.01	0.01	0.01	0.7	1.2	23	0.01
KL22-07	6.1	8.5	0.0015	15	0.28	1.1	99	24	15	0.01	0.01	0.01	1.2	2.6	24	0.01
KL22-07	8.5	11.5	0.0012	12	0.16	0.5	109	18	14	0.01	0.01	0.01	0.8	2.2	31	0.01
KL22-07	11.5	14.5	0.0027	27	0.07	0.01	152	229	22	0.01	0.01	3	1.5	4.9	35	0.01
KL22-07	14.5	17.5	0.0026	26	0.07	0.01	222	141	16	7	0.01	0.01	0.8	1.8	41	0.01
KL22-07	17.5	20.5	0.0011	11	0.1	0.01	89	19	15	0.01	0.01	0.01	0.9	1.4	37	0.01
KL22-07	20.5	23.5	0.0013	13	0.04	0.01	111	60	16	0.01	0.01	0.01	0.6	2.4	23	0.01
KL22-07	23.5	26.2	0.0166	166	0.04	0.01	106	51	30	0.01	0.01	0.01	0.6	3.0	24	0.01
KL22-07	26.2	29.1	0.087	870	0.02	1.4	87	170	6	16	5	0.01	0.8	8.6	38	0.01
KL22-07	29.1	32	0.054	540	0.02	0.6	105	61	15	8	2	6	0.6	5.1	73	0.01
KL22-07	32	35.5	0.0371	371	0.08	0.01	55	100	25	16	0.01	5	1.3	2.6	130	0.01
KL22-07	35.5	38.2	0.0266	266	0.06	2.6	266	230	50	12	0.01	6	4.3	5.5	75	0.01
KL22-07	38.2	41.5	0.073	730	0.25	33.8	34000	13400	130	16	6	0.01	19.2	193.0	55	0.39
KL22-07	41.5	48	0.021	210	0.1	2.3	336	180	37	71	7	0.01	2.3	11.9	102	0.01
KL22-07	48	51	0.0145	145	0.03	0.01	81	39	7	21	0.01	0.01	0.9	0.5	33	0.01
KL22-07	51	54.5	0.0098	98	0.01	0.01	47	49	4	19	0.01	0.01	0.7	0.0	25	0.01
KL22-07	54.5	56.5	0.0125	125	0.01	0.01	48	56	2	11	0.01	0.01	0.2	0.0	26	0.01
KL22-07	56.5	59.3	0.012	120	0.01	0.01	74	98	3	8	0.01	0.01	0.2	1.0	26	0.01
KL22-07	62.3	65.5	0.0086	86	0.01	0.01	60	45	3	7	0.01	0.01	0.01	0.9	18	0.01
KL22-07	65.5	68.5	0.0115	115	0.02	0.6	620	248	7	14	1	0.01	0.6	2.3	6	0.01
KL22-07	68.5	78.5	0.0176	176	0.08	0.9	378	1180	22	38	1	0.01	1.4	7.2	19	0.01
KL22-07	78.5	84.5	0.0122	122	0.01	4.5	1690	3950	2	7	0.01	0.01	4.5	2.1	23	0.01
KL22-07	84.5	87	0.0095	95	0.01	3.3	417	2400	7	11	1	0.01	2.7	0.9	27	0.01
KL22-07	87	90.2	0.0101	101	0.01	3.6	770	2190	27	10	0.01	0.01	4	1.4	26	0.01
KL22-07	90.2	93.8	0.0061	61	0.01	2.7	550	1950	13	15	0.01	0.01	3.3	1.5	25	0.01
KL22-07	93.8	97.2	0.0057	57	0.01	3.8	296	1950	8	7	4	0.01	1.5	2.0	30	0.01
KL22-07	97.2	100.1	0.0043	43	0.01	2.7	77	1070	3	7	3	0.01	1.4	1.1	25	0.01
KL22-07	100.1	102.7	0.007	70	0.01	1.9	384	630	4	3	1	0.01	0.9	1.0	27	0.01
KL22-07	102.7	105.8	0.0061	61	0.01	1.2	104	224	3	4	0.01	0.01	0.8	0.8	28	0.01
KL22-07	105.8	109.2	0.0101	101	0.01	2.3	342	750	5	6	0.01	0.01	0.9	0.8	26	0.01
KL22-07	109.2	112.6	0.0087	87	0.01	2.3	313	740	2	4	1	0.01	1.1	1.5	16	0.01
KL22-07	112.6	115.1	0.006	60	0.01	3.9	215	600	6	10	0.01	0.01	1.3	1.4	16	0.01
KL22-07	115.1	118.9	0.0059	59	0.01	6.2	324	276	6	6	0.01	0.01	1.2	0.9	12	0.01
KL22-07	118.9	121.7	0.0084	84	0.01	2.1	264	382	5	13	0.01	0.01	1	0.8	11	0.01
KL22-07	121.7	125.1	0.0164	164	0.01	1.2	263	331	3	8	0.01	0.01	0.9	0.5	12	0.01
KL22-07	125.1	128.5	0.008	80	0.01	0.7	84	104	2	6	0.01	0.01	0.01	0.8	15	0.01
KL22-07	128.5	132.2	0.0184	184	0.01	1.4	86	116	4	5	0.01	0.01	0.4	1.2	11	0.01
KL22-07	132.2	134.5	0.009	90	0.01	1.2	99	196	2	4	0.01	0.01	0.01	1.0	15	0.01
KL22-07	134.5	137.1	0.0041	41	0.01	1.1	96	137	3	4	0.01	0.01	0.4	0.6	12	0.01
KL22-07	137.1	140.2	0.0059	59	0.01	0.9	168	233	2	3	0.01	0.01	0.3	0.5	9	0.01
KL22-07	140.2	143.2	0.0049	49	0.01	0.6	147	124	4	6	0.01	0.01	0.3	1.0	12	0.01
KL22-07	143.2	146.2	0.0056	56	0.01	3.5	296	274	12	5	0.01	0.01	1.5	0.0	15	0.01
KL22-07	146.2	149	0.0051	51	0.01	1.5	303	296	3	4	0.01	0.01	0.7	0.5	9	0.01
KL22-07	149	151.7	0.0073	73	0.01	1.4	610	361	3	3	0.01	0.01	0.8	0.7	15	0.01
KL22-07	151.7	153.8	0.0091	91	0.02	2.6	720	1530	5	6	0.01	0.01	2.3	1.7	16	0.01
KL22-07	153.8	156.3	0.0082	82	0.03	1.9	420	1170	6	7	0.01	0.01	1	2.0	16	0.01
KL22-07	156.3	159	0.0068	68	0.01	1.7	430	1210	3	6	0.01	0.01	1.1	1.2	17	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL22-07	159	161.2	0.0093		93	0.02	4.1	1210	2010	20	32	0.01	0.01	3.5	1.5	11	0.01
KL22-07	161.2	163.7	0.0038		38	0.03	2.3	1120	780	9	11	0.01	0.01	2.3	2.0	14	0.01
KL22-07	163.7	166.5	0.0185		185	0.02	4.4	1580	2170	5	5	0.01	0.01	3.7	1.9	13	0.01
KL22-07	166.5	169.6	0.008		80	0.01	0.7	112	108	5	4	0.01	0.01	0.6	1.0	12	0.01
KL22-07	169.6	172.7	0.0025		25	0.13	19.7	3100	2600	12	6	0.01	0.01	2.8	10.2	14	0.01
KL22-07	172.7	174.6	0.0025		25	0.01	1.2	322	275	15	6	0.01	0.01	1.4	1.7	12	0.01
KL22-07	174.6	177.6	0.002		20	0.01	0.01	192	114	6	4	0.01	0.01	1	1.4	13	0.01
KL22-07	177.6	180.3	0.004		40	0.01	0.8	301	293	6	10	0.01	0.01	2.2	1.5	13	0.01
KL22-07	180.3	182.5	0.0103		103	0.02	0.6	460	750	23	23	0.01	2	0.8	2.9	15	0.01
KL22-07	182.5	185	0.0061		61	0.01	0.01	110	290	11	6	0.01	0.01	0.9	1.3	16	0.01
KL22-07	185	188	0.029		290	0.19	16.6	6510	9000	26	8	0.01	2	11.3	24.4	25	0.01
KL22-07	191.1	194.2	0.061		610	0.27	32.2	31000	37000	18	16	1	0.01	26.8	164.0	27	0.01
KL22-07	194.2	195.9	0.005		50	0.04	1	670	1570	5	4	0.01	0.01	0.3	2.5	17	0.01
KL22-07	195.9	198.5	0.0037		37	0.03	1.8	1140	2670	6	7	0.01	0.01	2.3	2.3	17	0.01
KL22-07	198.5	201	0.0058		58	0.04	2.1	890	2480	6	5	0.01	0.01	2.8	5.8	14	0.01
KL22-07	201	203.5	0.0306		306	0.04	0.9	460	1190	5	13	0.01	0.01	0.7	3.3	24	0.01
KL22-07	203.5	206.5	0.0127		127	0.05	1.3	690	840	14	9	6	0.01	1.3	6.3	26	0.01
KL22-07	206.5	208.5	0.0115		115	0.04	0.01	990	870	10	8	2	0.01	0.7	2.9	25	0.01
KL22-07	208.5	212.5	0.071		710	0.07	1.4	930	700	25	8	6	0.01	0.8	6.1	19	0.01
KL22-07	212.5	215.5	0.114		1140	0.5	11.2	3970	4140	120	9	56	4	1.8	118.0	32	0.01
KL22-07	215.5	218.5	0.45		4500	0.77	28.5	18200	7600	640	462	126	23	30.2	94.0	87	0.01
KL22-07	218.5	221.7	0.336		3360	0.17	3.9	820	332	800	69	5	6	60	11.5	185	0.01
KL22-07	221.7	224.5	0.0389		389	0.08	0.5	136	75	16	45	0.01	2	0.8	3.8	25	0.01
KL22-07	224.5	227.5	0.382		3820	0.52	3.6	346	263	420	500	4	14	58	26.5	118	0.01
KL22-07	227.5	229.5	0.534		5340	1.52	1.5	1190	112	45	46	3	24	3.9	8.2	21	0.01
KL22-07	229.5	232.5	0.97		9700	0.82	1.6	271	59	29	160	1	30	2.2	9.0	70	0.01
KL22-07	232.5	235.3	0.172		1720	0.31	0.01	215	37	30	1140	1	9	1.2	3.4	34	0.01
KL22-07	235.3	238.3	0.98		9800	1.07	2.8	198	66	66	1210	1	18	2.2	4.2	117	0.01
KL22-07	238.3	240.2	0.8		8000	0.7	1.8	255	77	38	950	0.01	15	1.5	10.3	158	0.01
KL22-07	240.2	241.5	1.08		10800	1.07	2.4	197	25	22	194	0.01	17	0.7	8.5	92	0.01
KL22-07	241.5	244.7	0.374		3740	0.51	2.1	570	169	43	780	2	9	4.4	5.7	51	0.11
KL22-07	244.7	249.5	0.51		5100	0.92	3.2	500	203	160	230	3	10	12	20.0	70	0.12
KL22-07	249.5	252.5	0.146		1460	0.42	0.8	146	29	18	850	0.01	6	1.6	7.5	74	0.01
KL22-07	252.5	257.5	0.082		820	1.68	0.6	242	58	48	540	1	5	1.6	8.9	80	0.01
KL22-07	257.5	260.5	0.066		660	0.67	0.01	105	32	44	1460	0.01	6	0.5	6.0	39	0.01
KL22-07	260.5	265	0.97		9700	0.85	2.4	5720	46	35	62	0.01	42	1.5	13.8	35	0.1
KL22-07	265	266.5	0.99		9900	1.52	9.4	10500	26	1450	302	5	11	36	18.8	58	0.58
KL22-07	266.5	269.5	4.74		47400	3.2	25.6	5700	25	830	115	4	17	24	28.8	58	0.13
KL22-07	269.5	271.7	1.47		14700	2.05	10.9	7200	10	8	33	1	11	0.01	17.3	30	0.01
KL22-07	271.7	273.7	0.84		8400	1	3.6	510	12	17	35	1	6	0.2	9.5	45	0.01
KL22-07	273.7	275	12.3		123000	10.9	6.8	4100	14	5	7	6	40	0.4	35.0	37	0.01
KL22-07	275	277.1	7.64		76400	6.67	2	810	7	2	6	2	64	0.01	36.2	40	0.01
KL22-07	277.1	280.8	2.55		25500	5.31	3.2	3400	15	2	93	36	19	0.3	65.0	66	0.01
KL22-07	280.8	283.7	0.6		6000	1.15	1.7	193	18	5	45	2	15	0.2	20.2	28	0.01
KL22-07	283.7	286.5	0.69		6900	0.56	0.8	2750	58	2	10	1	17	0.4	18.3	27	0.01
KL22-07	286.5	289.5	2.13		21300	2.61	2.1	128	10	2	79	0.01	38	0.01	9.5	32	0.01
KL22-07	289.5	292.5	2		20000	1.84	2.2	100	25	2	15	1	42	1	7.5	20	0.01
KL22-07	292.5	294.5	1.26		12600	1.08	1.4	62	15	4	3	0.01	26	0.3	8.0	30	0.01
KL22-07	294.5	296.5	1.73		17300	1.59	1.8	74	11	3	0.01	0.01	32	0.01	12.5	36	0.01
KL22-07	296.5	299.5	2.16		21600	1.53	2.8	332	100	68	3	1	40	1.1	18.0	56	0.11
KL22-07	299.5	302.5	3.59		35900	2.17	5.1	480	266	190	18	18	41	2	22.0	92	0.01
KL22-07	302.5	305.2	3.08		30800	2.75	10	910	247	480	13	8	28	15.3	21.0	103	0.01
KL22-07	305.2	308.1	5.41		54100	4.68	19.6	142	108	170	74	8	14	22	18.8	98	0.12
KL22-07	308.1	310.8	3.64		36400	0.86	17.9	274	182	400	245	34	11	35	11.0	24	0.21
KL22-07	310.8	312.4	1.03		10300	0.22	2.4	68	36	25	115	1	8	0.4	6.8	37	0.01
KL22-07	312.4	314	0.73		7300	0.16	1.9	50	17	8	163	0.01	5	0.5	5.7	61	0.1
KL22-07	314	317	0.421		4210	0.11	1.1	40	7	11	49	0.01	4	0.3	3.5	114	0.01
KL22-07	317	320	0.42		4200	0.14	0.9	34	7	4	83	0.01	3	0.01	4.4	47	0.01
KL22-07	320	323	0.487		4870	0.33	1.1	105	30	1	83	0.01	5	0.2	5.8	52	0.01
KL22-07	323	326	1.37		13700	0.51	2	68	22	2	139	0.01	7	0.01	5.5	49	0.01
KL22-07	326	329	0.479		4790	0.28	0.9	51	16	3	150	0.01	4	0.2	5.5	42	0.01
KL22-07	329	332.5	0.98		9800	0.33	1.6	870	128	36	406	0.01	7	1.6	7.0	45	0.15
KL22-07	332.5	335.5	0.63		6300	0.21	0.8	206	26	31	92	0.01	6	1.3	7.3	77	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL22-07	335.5	338.5	0.58	5800	0.28	0.7	129	12	23	66	0.01	5	0.8	6.0	112	0.01
KL22-07	338.5	341.5	0.98	9800	0.44	1.5	389	63	9	97	0.01	6	0.6	5.8	118	0.01
KL22-07	341.5	344.5	0.68	6800	0.41	1.1	327	15	10	265	0.01	5	0.3	7.3	81	0.01
KL22-07	344.5	347.8	1.8	18000	1.08	2.5	228	51	17	489	0.01	13	0.01	6.0	126	0.01
KL22-07	347.8	351.1	4.8	48000	2.58	5.1	128	16	1	381	1	48	0.01	12.0	43	0.01
KL22-07	351.1	353.6	6.3	63000	4.83	8.6	880	17	2	13	1	66	0.01	10.0	35	0.01
KL22-07	353.6	357.8	6.24	62400	3.44	7.9	1150	106	3	63	1	71	0.01	7.5	38	0.01
KL22-07	357.8	360.3	1.61	16100	1.4	3.6	216	70	13	187	1	46	0.01	17.5	30	0.01
KL22-07	360.3	362.6	0.53	5300	1.63	5.1	880	23	54	13	14	38	0.3	16.8	71	0.15
KL22-07	362.6	365.3	0.825	8250	1.67	2.3	12400	53	52	10	9	90	0.2	22.4	59	0.1
KL22-07	365.3	368.6	1.5	15000	1.58	4.8	13100	25	77	9	16	46	0.6	44.2	78	0.01
KL22-07	368.6	371.4	0.0316	316	0.11	0.6	460	45	17	5	2	2	0.01	1.4	15	0.01
KL22-07	371.4	374.4	0.0074	74	0.1	0.01	187	43	15	2	0.01	2	0.01	1.0	16	0.01
KL22-07	374.4	377.1	0.0223	223	0.13	0.01	388	22	26	0.01	0.01	2	0.01	2.4	13	0.01
KL22-07	377.1	380.5	0.34	3400	0.79	4.1	12700	1910	330	10	12	91	5.7	12.8	39	0.14
KL22-07	380.5	383.5	0.43	4300	0.65	2.7	500	45	50	8	4	73	1.8	10.8	29	0.01
KL22-07	383.5	386.5	0.22	2200	0.95	6.2	6400	55	310	7	26	45	1	9.0	47	0.1
KL22-07	386.5	391.2	0.0263	263	0.1	0.01	93	19	53	0.01	5	3	0.01	0.0	13	0.01
KL22-07	391.2	394.3	0.0049	49	0.01	0.01	83	19	4	0.01	1	3	0.3	0.0	8	0.01
KL22-07	394.3	397.4	0.0084	84	0.01	0.01	176	18	12	0.01	2	2	0.2	0.0	7	0.01
KL22-07	397.4	400	0.0148	148	0.01	0.01	95	15	19	2	2	2	0.01	0.0	11	0.01
KL22-07	400	403.1	0.0097	97	0.01	0.01	123	18	9	0.01	1	2	0.01	0.0	9	0.01
KL22-07	403.1	407.5	0.0051	51	0.01	0.01	68	25	7	0.01	1	3	0.3	0.0	9	0.01
KL22-07	407.5	410.5	0.0162	162	0.01	0.01	38	15	3	6	0.01	2	0.01	0.6	10	0.01
KL22-07	410.5	413.5	0.0334	334	0.04	0.01	213	214	39	6	1	2	0.9	3.4	17	0.01
KL22-07	413.5	417.7	0.0408	408	0.06	1.3	1040	500	12	8	11	3	0.4	2.1	14	0.01
KL22-07	417.7	421	0.006	60	0.04	0.01	51	34	23	0.01	0.01	2	0.2	0.6	12	0.01
KL22-07	421	422.5	0.0098	98	0.01	0.01	138	34	14	0.01	0.01	3	0.4	0.0	8	0.01
KL22-07	422.5	425.5	0.0114	114	0.03	0.01	115	16	16	0.01	1	2	0.4	0.0	11	0.01
KL22-07	425.5	428.5	0.0073	73	0.01	0.01	129	25	22	0.01	0.01	0.01	0.4	0.0	13	0.01
KL22-07	428.5	431.5	0.0074	74	0.01	0.01	59	43	27	7	0.01	0.01	0.3	0.0	25	0.01
KL22-07	431.5	434.5	0.003	30	0.01	0.01	29	25	18	0.01	0.01	0.01	0.3	0.0	21	0.01
KL22-07	434.5	436.3	0.0043	43	0.01	0.01	41	18	13	0.01	0.01	0.01	0.3	0.0	16	0.01
KL22-08	0	3	0.0013	13	0.02	0.01	45	22	5	0.01	0.01	0.01	0.5	1.0	23	0.12
KL22-08	3	6	0.003	30	0.09	0.01	138	34	5	2	0.01	0.01	0.6	0.8	19	0.01
KL22-08	6	9	0.0056	56	0.17	0.01	84	33	5	0.01	0.01	0.01	0.8	1.0	22	0.01
KL22-08	9	12	0.0032	32	1	2	135	30	18	0.01	0.01	0.01	1.5	4.0	25	0.01
KL22-08	12	15	0.0043	43	0.19	0.01	81	38	15	0.01	0.01	0.01	1.1	2.0	32	0.01
KL22-08	15	18	0.006	60	0.1	0.01	71	45	14	0.01	0.01	3	0.7	1.8	38	0.01
KL22-08	18	21	0.0107	107	0.11	0.7	293	500	18	14	0.01	2	1.4	4.3	47	0.01
KL22-08	21	23.8	0.0036	36	0.1	0.01	158	146	15	0.01	0.01	0.01	0.8	2.0	44	0.01
KL22-08	23.8	26.8	0.0017	17	0.03	0.01	86	23	9	0.01	0.01	0.01	0.4	1.3	24	0.01
KL22-08	26.8	29.1	0.0073	73	0.08	0.01	64	27	14	0.01	0.01	0.01	0.7	1.8	23	0.01
KL22-08	29.1	31.5	0.0038	38	0.08	0.01	162	83	19	0.01	0.01	0.01	0.5	2.0	25	0.01
KL22-08	31.5	34.5	0.0227	227	0.09	0.01	105	36	36	0.01	4	0.01	0.5	3.0	38	0.01
KL22-08	34.5	36	0.0108	108	0.01	0.8	187	174	14	0.01	2	0.01	0.5	11.5	49	0.01
KL22-08	36	39	0.0137	137	0.01	0.01	128	112	10	2	0.01	0.01	0.6	3.3	75	0.01
KL22-08	39	41.9	0.006	60	0.02	0.01	46	43	16	0.01	0.01	3	0.5	2.5	60	0.01
KL22-08	41.9	45	0.0219	219	0.06	0.01	51	36	17	7	0.01	4	1.3	3.5	75	0.01
KL22-08	45	48	0.031	310	0.51	21.7	36400	12500	94	16	30	4	8	126.0	52	1.18
KL22-08	48	52.5	0.0089	89	0.15	13.8	4000	1830	32	17	36	0.01	4.3	44.3	36	0.15
KL22-08	52.5	56.5	0.0084	84	0.33	5	6900	1890	130	35	8	0.01	2.8	7.6	39	0.2
KL22-08	56.5	60	0.0185	185	0.48	7.1	15200	6900	270	46	8	0.01	4.9	8.6	40	0.34
KL22-08	60	65.5	0.0138	138	0.44	3.8	6000	3400	44	7	0.01	0.01	3.1	8.8	33	0.17
KL22-08	65.5	68.5	0.004	40	0.08	1.1	2510	1620	8	6	0.01	0.01	1.5	4.8	17	0.01
KL22-08	68.5	70.8	0.006	60	0.02	0.9	2460	1560	9	4	0.01	0.01	1	4.5	21	0.01
KL22-08	70.8	73.3	0.0047	47	0.01	0.8	1510	940	5	8	0.01	0.01	0.6	3.5	15	0.01
KL22-08	73.3	75.3	0.0057	57	0.01	0.7	1000	680	8	35	0.01	0.01	0.8	3.3	24	0.1
KL22-08	75.3	78.6	0.0069	69	0.01	0.9	1480	1280	17	27	0.01	0.01	1.8	6.0	26	0.01
KL22-08	78.6	80.1	0.0065	65	0.01	1	590	416	14	41	0.01	0.01	1.4	3.0	19	0.01
KL22-08	80.1	83	0.0028	28	0.01	1.5	88	72	4	33	0.01	0.01	0.8	0.8	10	0.01
KL22-08	83	85.8	0.0032	32	0.01	0.9	930	810	9	80	1	0.01	2.8	3.5	9	0.01
KL22-08	85.8	88.6	0.0025	25	0.01	0.9	700	1450	5	135	2	0.01	2	4.7	12	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL22-08	88.6	93	0.0024		24	0.12	0.8	275	194	46	7	0.01	0.01	0.8	1.0	13	0.01
KL22-08	93	95.3	0.0012		12	0.01	1.3	480	450	6	8	0.01	0.01	0.9	0.6	25	0.01
KL22-08	95.3	98.2	0.004		40	0.03	3.3	2400	1850	9	5	0.01	0.01	1.4	1.0	22	0.01
KL22-08	98.2	101.7	0.0009		9	0.01	0.8	164	198	7	0.01	0.01	0.01	0.4	1.3	23	0.01
KL22-08	101.7	105	0.0015		15	0.01	1.5	570	420	6	0.01	2	0.01	0.2	2.0	25	0.1
KL22-08	105	110.3	0.0016		16	0.01	0.01	135	91	27	2	0.01	0.01	0.3	0.8	23	0.01
KL22-08	110.3	113.3	0.002		20	0.01	1.3	256	490	2	0.01	2	0.01	0.2	1.5	27	0.01
KL22-08	113.3	116.8	0.0009		9	0.01	1.3	90	240	1	3	0.01	0.01	0.4	1.2	27	0.01
KL22-08	116.8	119.2	0.0006		6	0.01	1	41	110	2	0.01	0.01	0.01	0.01	0.5	24	0.01
KL22-08	119.2	122.8	0.0012		12	0.01	2.9	147	242	3	3	0.01	0.01	0.4	1.0	27	0.01
KL22-08	122.8	125.9	0.0017		17	0.01	5.4	308	1440	2	0.01	0.01	0.01	1.2	1.5	25	0.01
KL22-08	125.9	127.5	0.0067		67	0.04	23.6	2000	2560	35	7	0.01	4	5.1	4.8	28	0.01
KL22-08	127.5	131	0.0045		45	0.01	3.1	590	430	36	7	0.01	0.01	1	2.0	25	0.01
KL22-08	131	133.6	0.0017		17	0.01	1.8	63	358	2	4	1	0.01	0.4	0.5	22	0.01
KL22-08	133.6	136	0.0016		16	0.01	1.3	141	530	3	0.01	0.01	0.01	0.5	0.8	22	0.01
KL22-08	136	138.5	0.0028		28	0.01	6.1	700	2040	6	3	0.01	0.01	4	1.4	19	0.01
KL22-08	138.5	142.3	0.0022		22	0.01	2.1	253	189	4	10	0.01	0.01	0.7	0.8	16	0.01
KL22-08	142.3	146	0.0007		7	0.01	2	75	58	6	23	0.01	0.01	0.4	0.5	14	0.01
KL22-08	146	148.4	0.0005		5	0.01	1.9	158	240	3	6	0.01	0.01	0.5	0.5	9	0.1
KL22-08	148.4	151.5	0.001		10	0.01	1	64	109	1	4	0.01	0.01	0.01	0.5	10	0.01
KL22-08	151.5	154.6	0.0006		6	0.01	1.1	101	113	3	2	0.01	0.01	0.3	0.5	11	0.01
KL22-08	154.6	156	0.0012		12	0.01	1.5	81	146	2	0.01	0.01	0.01	0.3	0.0	12	0.01
KL22-08	156	159	0.0017		17	0.01	0.01	54	38	3	5	0.01	0.01	0.2	0.5	10	0.01
KL22-08	159	162	0.0011		11	0.01	0.01	71	100	2	2	0.01	0.01	0.2	1.0	15	0.01
KL22-08	162	165	0.0007		7	0.01	0.01	73	128	3	4	0.01	0.01	0.2	1.4	14	0.01
KL22-08	165	167.6	0.0011		11	0.01	0.8	70	219	3	2	0.01	0.01	0.01	1.0	10	0.01
KL22-08	167.6	171	0.0071		71	0.01	0.8	235	269	7	5	0.01	0.01	0.7	0.8	14	0.01
KL22-08	171	174	0.0012		12	0.02	1.1	112	109	9	8	0.01	0.01	1	1.5	20	0.01
KL22-08	174	177	0.0012		12	0.01	1.7	141	159	4	6	0.01	0.01	0.6	1.3	17	0.01
KL22-08	177	180	0.0011		11	0.01	1.7	140	200	4	0.01	0.01	0.01	0.3	1.3	12	0.01
KL22-08	180	183	0.0026		26	0.01	2.3	183	260	3	2	0.01	0.01	0.4	1.8	18	0.01
KL22-08	183	186.5	0.0027		27	0.02	4.2	311	345	3	2	0.01	0.01	1	1.3	20	0.01
KL22-08	186.5	189.5	0.0013		13	0.01	0.9	78	215	3	3	0.01	0.01	0.7	1.3	17	0.01
KL22-08	189.5	193.2	0.0012		12	0.01	2.3	1440	680	3	4	0.01	0.01	1.2	1.0	19	0.01
KL22-08	193.2	196.2	0.001		10	0.01	1.3	111	209	2	0.01	0.01	0.01	0.5	0.8	18	0.01
KL22-08	196.2	199.3	0.0024		24	0.01	1.5	195	270	6	15	0.01	0.01	0.6	1.5	13	0.01
KL22-08	199.3	202.8	0.0037		37	0.01	1.6	343	670	4	8	0.01	0.01	0.9	1.3	15	0.01
KL22-08	202.8	204.6	0.0024		24	0.01	0.01	178	173	5	6	3	0.01	0.3	1.7	17	0.01
KL22-08	204.6	207	0.0012		12	0.01	0.01	53	90	6	5	0.01	0.01	0.3	1.0	21	0.01
KL22-08	207	210	0.0015		15	0.01	0.5	168	184	4	5	0.01	0.01	0.5	1.8	14	0.01
KL22-08	210	213	0.0016		16	0.01	0.7	118	179	6	3	0.01	0.01	1.3	1.0	18	0.01
KL22-08	213	216	0.0059		59	0.02	7	2800	2900	6	3	0.01	0.01	5.2	7.5	13	0.01
KL22-08	216	219	0.0054		54	0.01	0.01	163	270	16	21	0.01	0.01	0.5	1.5	19	0.01
KL22-08	219	222	0.0015		15	0.01	0.01	117	220	6	4	0.01	3	0.7	1.3	21	0.01
KL22-08	222	225	0.0029		29	0.01	1.1	218	980	10	6	0.01	2	0.6	7.5	21	0.01
KL22-08	225	227.7	0.0064		64	0.03	7.3	4400	4400	10	5	0.01	2	6.2	12.3	17	0.01
KL22-08	227.7	230.7	0.0123		123	0.12	23.7	3500	18000	12	15	46	0.01	4.3	49.4	21	0.01
KL22-08	230.7	233.7	0.0038		38	0.05	4.3	700	2100	19	12	12	0.01	0.7	2.6	14	0.01
KL22-08	233.7	236	0.0245		245	0.07	2.2	1300	1940	44	29	6	0.01	3.2	3.3	20	0.11
KL22-08	236	239.1	0.0102		102	0.03	2.1	1500	1520	29	8	3	0.01	2.5	4.3	21	0.01
KL22-08	239.1	243	0.0046		46	0.02	0.01	366	376	8	14	1	0.01	0.2	2.2	18	0.01
KL22-08	243	246	0.0095		95	0.07	4.4	2600	3680	21	10	1	3	5.9	9.8	27	0.01
KL22-08	246	249	0.0175		175	0.05	1.3	990	540	16	8	6	0.01	0.8	4.5	22	0.01
KL22-08	249	254.1	0.121		1210	0.3	8.5	12900	1130	31	6	163	9	1.5	65.0	24	0.01
KL22-08	254.1	256.3	0.41		4100	1.04	9.5	18400	450	45	10	72	21	2.1	48.8	30	0.01
KL22-08	256.3	257.8	0.463		4630	0.59	1.6	197	34	30	158	15	10	2.4	8.0	56	0.01
KL22-08	257.8	259	0.091		910	0.05	1.6	4100	73	33	23	3	2	21	5.4	321	0.23
KL22-08	259	261	0.214		2140	0.09	0.6	62	43	47	163	2	4	8.7	10.4	276	0.01
KL22-08	261	264	0.214		2140	0.37	2	1400	127	53	496	20	12	8.5	45.5	201	0.1
KL22-08	264	267	0.087		870	0.19	1.1	124	56	13	810	5	6	1.6	7.0	62	0.01
KL22-08	267	270	0.429		4290	0.49	1.9	1420	62	46	230	12	12	2	10.8	72	0.01
KL22-08	270	273	0.28		2800	0.51	1.6	10300	71	32	202	410	18	1.9	37.5	79	0.01
KL22-08	273	275.55	0.78		7800	0.67	16.5	9300	1800	290	356	55	17	125	54.2	201	0.7

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL24-01	503.8	506.8														
KL24-02	1.5	13.5														
KL24-02	13.5	16.7														
KL24-02	16.7	19.25														
KL24-02	19.25	22.7														
KL24-02	22.7	25.45														
KL24-02	25.45	28.9														
KL24-02	28.9	31.15														
KL24-02	31.15	34.6														
KL24-02	34.6	37.45														
KL24-02	37.45	40.2														
KL24-02	40.2	43														
KL24-02	43	46.6														
KL24-02	46.6	49.4														
KL24-02	49.4	52.55														
KL24-02	52.55	55.65														
KL24-02	55.65	58.5														
KL24-02	58.5	61.6														
KL24-02	61.6	64.8														
KL24-02	64.8	67.7														
KL24-02	70.2	73.25														
KL24-02	73.25	76.8														
KL24-02	76.8	80.3														
KL24-02	80.3	83.8														
KL24-02	83.8	87.3														
KL24-02	87.3	90.8														
KL24-02	90.8	94.3														
KL24-02	94.3	97.8														
KL24-02	97.8	101.3														
KL24-02	101.3	104.8														
KL24-02	104.8	108.3														
KL24-02	108.3	111.8														
KL24-02	111.8	115.3														
KL24-02	115.3	118.8														
KL24-02	118.8	122.3														
KL24-02	122.3	125.8														
KL24-02	125.8	129.3														
KL24-02	129.3	132.8														
KL24-02	132.8	136.3														
KL24-02	136.3	139.8														
KL24-02	139.8	143.3														
KL24-02	143.3	146.8														
KL24-02	146.8	150.3														
KL24-02	150.3	153.8														
KL24-02	153.8	157.3														
KL24-02	157.3	160.8														
KL24-02	160.8	164.3														
KL24-02	164.3	167.8														
KL24-02	167.8	171.3														
KL24-02	171.3	174.8														
KL24-02	174.8	178.3														
KL24-02	178.3	181.8														
KL24-02	181.8	185.3														
KL24-02	185.3	188.8														
KL24-02	188.8	192.3														
KL24-02	192.3	195.8														
KL24-02	195.8	199.3														
KL24-02	199.3	202.8														
KL24-02	202.8	206.3														
KL24-02	206.3	209.8														
KL24-02	209.8	213.3														
KL24-02	213.3	216.8														
KL24-02	216.8	220.3														
KL24-02	220.3	223.8														
KL24-02	223.8	227.3														
KL24-02	227.3	230.8														
KL24-02	230.8	234.3														
KL24-02	234.3	237.8														
KL24-02	237.8	241.3														
KL24-02	241.3	244.8														
KL24-02	244.8	248.3														
KL24-02	248.3	251.8														
KL24-02	251.8	255.3														
KL24-02	255.3	258.8														
KL24-02	258.8	262.3														
KL24-02	262.3	265.8														
KL24-02	265.8	269.3														
KL24-02	269.3	272.8														
KL24-02	272.8	276.3														
KL24-02	276.3	279.8														
KL24-02	279.8	283.3														
KL24-02	283.3	286.8														
KL24-02	286.8	290.3														
KL24-02	290.3	293.8														
KL24-02	293.8	297.3														
KL24-02	297.3	300.8														
KL24-02	300.8	304.3														
KL24-02	304.3	307.8														
KL24-02	307.8	311.3														
KL24-02	311.3	314.8														
KL24-02	314.8	318.3														
KL24-02	318.3	321.8														
KL24-02	321.8	325.3														
KL24-02	325.3	328.8														
KL24-02	328.8	332.3														
KL24-02	332.3	335.8														
KL24-02	335.8	339.3														
KL24-02	339.3	342.8														
KL24-02	342.8	346.3														
KL24-02	346.3	349.8														
KL24-02	349.8	353.3														
KL24-02	353.3	356.8														
KL24-02	356.8	360.3														
KL24-02	360.3	363.8														
KL24-02	363.8	367.3														
KL24-02	367.3	370.8														
KL24-02	370.8	374.3														
KL24-02	374.3	377.8														
KL24-02	377.8	381.3														
KL24-02	381.3	384.8														
KL24-02	384.8	388.3														
KL24-02	388.3	391.8														
KL24-02	391.8	395.3														
KL24-02	395.3	398.8														
KL24-02	398.8	402.3														
KL24-02	402.3	405.8														
KL24-02	405.8	409.3														
KL24-02	409.3	412.8														
KL24-02	412.8	416.3														
KL24-02	416.3	419.8														
KL24-02	419.8	423.3														
KL24-02	423.3	426.8														
KL24-02	426.8	430.3														
KL24-02	430.3	433.8														
KL24-02	433.8	437.3														
KL24-02	437.3	440.8														
KL24-02	440.8	444.3														
KL24-02	444.3	447.8														
KL24-02	447.8	451.3														
KL24-02	451.3	454.8														
KL24-02	454.8	458.3														
KL24-02	458.3	461.8														
KL24-02	461.8	465.3														

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL24-03	43.65	47														
KL24-03	47	49.5														
KL24-03	49.5	52.4														
KL24-03	52.4	55.65														
KL24-03	55.65	58.5														
KL24-03	58.5	61.5														
KL24-03	61.5	64.15														
KL24-03	64.15	67.15														
KL24-03	67.15	71.65														
KL24-03	127.9	130.25														
KL24-03	153.7	155														
KL24-03	163.9	165.1														
KL24-03	167.9	181.4														
KL24-03	181.4	184.5														
KL24-03	184.5	187.1														
KL24-03	187.1	190.3														
KL24-03	190.3	195														
KL24-03	195	198														
KL24-03	198	201.25														
KL24-03	201.25	204														
KL24-03	204	207														
KL24-03	207	210														
KL24-03	210	213	0.22	2200	0.77	1.8	1340	77	88	540	14	4	2.1	12.7	60	0.19
KL24-03	213	216	1.03	10300	1.59	4.3	315	31	9	211	83	8	0.5	13.0	78	0.1
KL24-03	216	218.85	0.262	2620	0.81	1.8	760	24	9	283	56	7	0.4	9.5	43	0.01
KL24-03	218.85	222	0.234	2340	0.75	1.8	2060	15	31	48	53	6	0.2	16.0	36	0.01
KL24-03	222	224.15	0.235	2350	1.32	1.8	500	44	29	16	36	2	1.2	21.5	23	0.01
KL24-03	224.15	228.7	0.391	3910	0.44	1.5	151	87	11	340	117	13	0.7	37.3	104	0.01
KL24-03	228.7	231.7	0.243	2430	1.23	2	256	34	10	137	93	6	0.5	34.5	21	0.01
KL24-03	231.7	234	0.122	1220	0.64	1	43	20	15	67	12	7	1.3	20.4	15	0.01
KL24-03	234	237	0.282	2820	0.84	0.8	43	18	13	49	16	10	0.01	38.1	16	0.01
KL24-03	237	240	0.239	2390	0.86	0.6	41	11	40	18	53	17	0.3	40.0	19	0.01
KL24-03	240	243	0.361	3610	1	0.8	41	10	5	52	6	12	0.01	36.5	11	0.01
KL24-03	243	247.05	0.276	2760	1.58	0.8	57	12	4	65	12	10	0.01	40.0	15	0.01
KL24-03	247.05	250.5	0.335	3350	0.73	0.8	72	16	3	68	2	11	0.01	18.5	23	0.01
KL24-03	250.5	253.5	0.376	3760	0.56	1.2	61	19	2	19	3	15	0.01	32.0	32	0.01
KL24-03	253.5	257.4	0.477	4770	0.61	1.3	140	22	4	73	0.01	91	0.4	23.0	24	0.01
KL24-03	257.4	260.4	0.71	7100	0.62	1.4	113	86	1	12	0.01	49	0.01	10.3	48	0.01
KL24-03	260.4	263.4	1.84	18400	1.18	3.2	141	33	1	92	0.01	50	0.01	16.0	70	0.01
KL24-03	263.4	265.9	3.68	36800	2.56	5.5	230	90	3	23	1	35	0.01	22.5	96	0.01
KL24-03	265.9	268.1	3.04	30400	3.96	4.1	127	36	1	21	1	18	0.01	25.0	89	0.01
KL24-03	268.1	271.5	2.13	21300	3.34	3	72	13	1	309	0.01	14	0.01	17.5	74	0.01
KL24-03	271.5	275.7	0.86	8600	0.52	1.6	73	23	0.01	300	0.01	9	0.01	8.0	68	0.1
KL24-03	275.7	278.7	1.2	12000	0.58	2.6	144	110	360	210	0.01	7	0.9	10.0	86	0.17
KL24-03	278.7	282	1.85	18500	1.5	3.2	78	48	0.01	96	0.01	9	0.3	10.0	73	0.01
KL24-03	282	285.8	1.79	17900	1.28	2.5	80	97	80	106	0.01	12	0.2	8.0	91	0.16
KL24-03	285.8	288	1.89	18900	1.2	2.8	103	32	4	138	0.01	16	0.6	11.5	75	0.1
KL24-03	288	291	1.7	17000	1.07	2.7	81	24	2	164	0.01	11	0.01	10.0	89	0.01
KL24-03	291	294	1.82	18200	1.26	4.2	51	63	6	167	0.01	12	0.01	11.0	82	0.41
KL24-03	294	297	1.92	19200	0.81	7.2	440	157	33	144	2	11	0.9	10.0	79	0.49
KL24-03	297	300	1.89	18900	1.75	4.3	198	290	610	115	2	13	2.6	11.0	79	0.18
KL24-03	300	303	1.72	17200	1.21	3.2	78	19	23	230	3	8	0.01	7.3	89	0.01
KL24-03	303	306	0.95	9500	0.64	1.8	42	16	3	115	1	8	0.01	8.5	76	0.01
KL24-03	306	309	1.58	15800	1.08	2.7	79	25	11	114	2	9	0.01	9.0	76	0.01
KL24-03	309	312	1.47	14700	1.24	2.5	63	20	0.01	25	3	8	0.01	7.5	90	0.01
KL24-03	312	315	0.58	5800	0.54	1	53	12	1	63	0.01	7	0.01	5.3	90	0.01
KL24-03	315	318	0.96	9600	0.82	1.4	60	16	1	109	0.01	8	0.01	6.8	93	0.01
KL24-03	318	321	1.1	11000	0.95	1.8	74	43	1	180	0.01	9	0.01	6.5	86	0.01
KL24-03	321	324	0.92	9200	0.63	4.6	1770	1270	29	173	0.01	9	22	11.0	103	0.01
KL24-03	324	327	0.98	9800	1.06	2.2	61	34	3	153	1	12	0.01	7.0	95	0.1
KL24-03	327	330	1.23	12300	1.03	3.2	207	77	89	360	1	14	1.2	10.0	82	0.18
KL24-03	330	333	1.24	12400	1.11	2.7	89	92	34	236	2	10	1.3	8.5	83	0.24
KL24-03	333	336	1.33	13300	1.29	2.8	480	125	4	346	1	11	0.01	6.4	65	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL24-03	517.65	520.65														
KL24-03	520.65	523.55														
KL24-03	523.55	526.3														
KL24-03	526.3	528														
KL24-03	528	532.5														
KL24-03	532.5	535.6														
KL24-03	535.6	538														
KL24-03	538	541														
KL24-03	541	544.5														
KL24-03	544.5	547.5														
KL24-03	547.5	550.25														
KL24-03	553.9	564.5														
KL24-03	564.5	568.35														
KL24-03	568.35	571.35														
KL24-03	571.35	574.4														
KL24-03	574.4	577.4														
KL24-03	577.4	580.45														
KL24-03	580.45	583.45														
KL24-03	586.6	598.3														
KL24-03	598.3	601.65														
KL24-03	601.65	604.45														
KL24-03	604.45	607.65														
KL24-03	607.65	610.4														
KL24-03	610.4	613														
KL24-03	613	616.5														
KL24-03	616.5	619														
KL24-03	619	622.35														
KL24-03	622.35	625.5														
KL24-03	625.5	628.5														
KL24-03	628.5	631.7														
KL24-03	631.7	634.65														
KL24-03	634.65	637.4														
KL24-03	637.4	640.3														
KL24-03	640.3	643.5														
KL24-03	643.5	646.7														
KL24-03	646.7	649.8														
KL24-03	649.8	652.5														
KL24-03	652.5	655.8														
KL24-03	655.8	658.5														
KL24-03	658.5	661.5														
KL24-03	661.5	664.5														
KL24-03	664.5	667.65														
KL24-03	667.65	670.8														
KL24-03	673.3	676.4	0.35	3500	0.14	0.7	42	7	0.01	150	0.01	8	0.2	7.3	23	0.01
KL24-03	676.4	679.4	1.09	10900	0.53	1	151	1	1	13	0.01	21	0.01	8.5	66	0.01
KL24-03	679.4	681.6	0.93	9300	0.53	1.6	103	5	1	440	0.01	21	0.5	9.3	51	0.01
KL24-03	681.6	685.2	1.04	10400	0.52	1.5	98	5	3	59	0.01	22	0.01	9.4	55	0.01
KL24-03	685.2	689.2	0.65	6500	0.31	1	66	1	1	46	0.01	15	0.01	6.0	44	0.01
KL24-03	689.2	692.1	0.279	2790	0.16	0.8	33	1	1	28	0.01	8	0.01	3.3	33	0.01
KL24-03	692.1	694.2	0.162	1620	0.05	0.6	23	1	1	20	0.01	7	0.01	3.0	93	0.01
KL24-03	694.2	697	0.091	910	0.01	0.6	16	1	1	372	0.01	6	0.01	1.3	240	0.01
KL24-03	697	700.7	1.1	11000	0.33	3.2	100	5	0.01	121	0.01	23	0.01	26.3	41	0.01
KL24-03	700.7	703.5	0.264	2640	0.08	0.1	23	5	0.01	58	0.01	5	0.01	4.0	26	0.01
KL24-03	703.5	706.5	0.089	890	0.04	0.1	14	1	2	69	0.01	3	0.01	1.5	20	0.01
KL24-03	706.5	709.25	0.22	2200	0.06	0.6	20	1	0.01	183	0.01	2	0.01	3.5	51	0.01
KL24-03	709.25	712.5	0.243	2430	0.1	1.2	65	30	19	180	0.01	8	6.2	2.2	240	0.12
KL24-03	712.5	715.5	0.275	2750	0.06	1.4	166	11	11	192	1	7	3.1	4.1	293	0.11
KL24-03	715.5	718.5	0.158	1580	0.05	0.1	18	1	1	310	0.01	1	0.01	2.3	32	0.01
KL24-03	718.5	721.5	0.266	2660	0.11	1	510	90	13	295	0.01	8	3	3.8	120	0.14
KL24-03	721.5	724.5	0.49	4900	0.26	1	37	6	2	440	0.01	9	0.01	7.9	208	0.01
KL24-03	724.5	727.5	0.338	3380	0.18	0.1	22	1	4	295	0.01	4	0.01	4.7	237	0.01
KL24-03	727.5	730.5	0.21	2100	0.06	0.1	30	7	3	390	0.01	7	0.6	3.4	32	0.01
KL24-03	730.5	733.5	0.17	1700	0.05	0.1	18	1	0.01	303	0.01	11	0.01	2.0	26	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL24-03	733.5	736.5	0.157		1570	0.02	0.6	31	5	3	410	0.01	5	0.01	2.3	38	0.01
KL24-03	736.5	739.5	0.523		5230	0.1	1	28	1	0.01	490	0.01	8	0.01	4.5	16	0.01
KL24-03	739.5	742.5	0.75		7500	0.22	2.1	96	9	11	326	0.01	15	1.3	4.8	14	0.01
KL24-03	742.5	745.5	0.71		7100	0.23	2.2	86	41	0.01	225	0.01	6	0.01	4.9	13	0.01
KL24-03	745.5	747.45	0.341		3410	0.14	0.8	45	11	2	224	0.01	15	0.01	5.3	17	0.01
KL24-03	747.45	751.5	0.335		3350	0.19	0.9	40	5	4	96	0.01	15	0.01	4.1	18	0.01
KL24-03	751.5	754.5	0.59		5900	0.26	3.1	72	22	5	103	0.01	13	0.01	7.0	11	0.01
KL24-03	754.5	757.5	0.68		6800	0.51	2.1	128	8	5	272	0.01	16	0.01	8.0	17	0.01
KL24-03	757.5	760.5	0.76		7600	0.42	2	101	1	2	25	0.01	16	0.01	9.2	23	0.01
KL24-03	760.5	763.5	0.149		1490	0.19	0.7	32	1	1	184	0.01	12	0.01	4.3	12	0.01
KL24-03	763.5	766.5	0.273		2730	0.02	0.1	17	1	0.01	152	0.01	3	0.01	3.5	12	0.01
KL24-03	766.5	768.9	0.183		1830	0.06	0.5	27	1	10	84	0.01	10	0.01	2.5	8	0.01
KL24-03	768.9	772.5	1.32		13200	0.67	2.3	194	6	3	91	0.01	34	0.01	12.8	23	0.01
KL24-03	772.5	775.5	1.15		11500	0.73	2.5	202	6	2	33	1	38	0.01	10.0	29	0.01
KL24-03	775.5	778.5	1.83		18300	0.96	4.4	219	1	2	97	0.01	36	0.01	11.9	16	0.01
KL24-03	778.5	781.5	2.94		29400	1.56	8.2	393	6	3	59	0.01	48	0.01	17.0	29	0.01
KL24-03	781.5	784.5	1.61		16100	0.83	4.9	395	5	3	159	0.01	43	0.01	9.7	35	0.01
KL24-03	784.5	787.5	1.84		18400	0.85	6	283	6	3	49	0.01	27	0.01	9.5	26	0.01
KL24-03	787.5	790.5	2.07		20700	0.92	7.2	480	7	5	31	0.01	69	0.01	13.5	38	0.01
KL24-03	790.5	793.5	1.66		16600	1.54	7.4	530	13	4	460	0.01	46	0.01	16.9	38	0.01
KL24-03	793.5	796.5	0.74		7400	0.36	2.9	212	6	5	94	0.01	26	0.01	12.0	32	0.01
KL24-03	796.5	799.5	1.2		12000	0.63	4.4	277	8	6	168	0.01	26	0.01	9.5	40	0.01
KL24-03	799.5	801.2	0.97		9700	0.59	6.7	720	5	10	26	0.01	22	0.3	11.7	30	0.01
KL24-03	801.2	804.1	1		10000	0.56	6.6	440	7	7	61	0.01	31	0.01	15.3	50	0.01
KL24-03	804.1	808.5	1.02		10200	0.45	5.8	660	1	5	63	0.01	25	0.01	12.3	26	0.01
KL24-03	808.5	811.25	1		10000	0.43	5.8	680	1	6	15	1	23	0.01	8.3	30	0.01
KL24-03	811.25	814.5	1.62		16200	0.86	5.7	368	1	3	136	1	47	0.01	14.5	22	0.01
KL24-03	814.5	817.5	1.27		12700	0.61	4.1	206	1	13	32	0.01	47	0.01	11.5	30	0.01
KL24-03	817.5	820.5	1.52		15200	0.64	4.1	268	1	2	66	0.01	39	0.01	13.2	30	0.01
KL24-03	820.5	823.5	1.74		17400	1.07	8.4	680	6	3	30	1	60	0.01	15.0	32	0.01
KL24-03	823.5	826.5	0.98		9800	0.59	8.5	1530	7	3	40	0.01	32	0.01	16.8	30	0.01
KL24-03	826.5	829.5	0.75		7500	0.38	6.2	460	6	4	22	0.01	23	0.01	15.3	28	0.01
KL24-03	829.5	832	0.513		5130	0.59	4.1	710	10	5	95	1	20	0.01	17.8	52	0.01
KL24-03	832	835.5	0.175		1750	0.07	1.7	208	7	2	14	0.01	12	0.01	4.5	26	0.01
KL24-03	835.5	838.5	0.12		1200	0.04	1.5	189	8	1	6	0.01	17	0.01	2.3	22	0.01
KL24-03	838.5	841.5	0.22		2200	0.1	3.4	248	6	1	21	1	14	0.01	4.5	15	0.01
KL24-03	841.5	844.5	0.501		5010	0.2	3.5	367	7	2	9	1	22	0.4	9.0	11	0.01
KL24-03	844.5	845.9	0.108		1080	0.09	1.6	176	6	3	4	0.01	10	0.2	3.0	13	0.01
KL24-03	845.9	847.5	0.96		9600	0.81	6.2	269	7	10	88	0.01	22	0.7	10.5	25	0.01
KL24-03	847.5	850.5	0.73		7300	0.4	10.8	370	36	310	51	0.01	19	16	9.9	49	0.15
KL24-03	850.5	853.5	1.08		10800	0.69	7.9	142	19	25	9	2	32	3.4	11.9	34	0.01
KL24-03	853.5	857	1.43		14300	0.89	6.1	267	7	5	9	1	29	0.3	8.9	31	0.01
KL24-03	857	860	1.64		16400	0.97	7.3	245	9	10	58	0.01	34	0.2	13.2	30	0.01
KL24-03	860	863	0.61		6100	0.36	3.2	94	6	18	121	0.01	16	0.01	7.0	36	0.01
KL24-03	863	866	1.76		17600	1.05	7.7	402	7	10	42	0.01	36	0.7	11.5	53	0.01
KL24-03	866	869	1.65		16500	1.11	6.8	293	7	4	33	1	44	1.4	10.4	54	0.01
KL24-03	869	872	3.34		33400	1.41	16.1	1220	8	7	76	0.01	61	0.01	18.0	57	0.01
KL24-03	872	874	2.24		22400	1.68	15.2	1070	5	3	26	1	46	0.01	12.0	59	0.01
KL24-03	874	876	1.92		19200	1.07	12	900	6	6	23	0.01	36	0.3	9.5	63	0.01
KL24-03	876	879	1.33		13300	0.54	7.3	375	7	5	86	2	26	0.01	13.5	40	0.01
KL24-03	879	882	0.62		6200	0.27	4.6	328	8	7	134	2	17	0.01	21.3	36	0.01
KL24-03	882	885															
KL24-03	885	888															
KL24-03	888	891.5															
KL24-03	891.5	895															
KL24-03	895	898															
KL24-03	898	901															
KL24-03	901	904															
KL24-05	0	2.5	0.0018		18	0.01	0.1	31	44	2	1	0.01	1	0.01	0.0	22	0.01
KL24-05	2.5	5.5	0.0051		51	0.01	0.1	117	87	7	3	0.01	2	0.5	0.9	24	0.01
KL24-05	5.5	8.5	0.0021		21	0.02	0.9	140	57	24	2	0.01	1	1.2	1.4	25	0.01
KL24-05	8.5	11.5	0.0021		21	0.01	0.1	41	33	6	1	0.01	2	0.2	0.7	21	0.01
KL24-05	11.5	14.5	0.0037		37	0.01	0.1	36	41	4	1	0.01	1	0.2	0.0	14	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL24-05	14.5	17.5	0.003		30	0.01	0.1	52	37	8	1	0.01	1	0.6	0.9	27	0.01
KL24-05	17.5	21.3	0.0033		33	0.01	0.1	56	57	20	1	0.01	1	0.8	2.3	27	0.01
KL24-05	21.3	25	0.024		240	0.03	0.1	87	171	18	1	0.01	1	1	4.8	33	0.01
KL24-05	25	28	0.0034		34	0.05	1.3	183	730	17	1	0.01	4	0.8	5.5	71	0.01
KL24-05	28	31	0.0072		72	0.08	4	254	820	39	1	0.01	3	1.3	3.6	62	0.01
KL24-05	31	34	0.027		270	1.12	20.1	6500	4940	200	36	32	2	8	21.8	42	0.44
KL24-05	34	37	0.05		500	3.4	29.8	23900	6020	680	44	64	4	19.6	28.4	170	2.16
KL24-05	37	39.7	0.0141		141	0.09	2.6	2410	1900	160	20	3	3	1.2	1.7	30	0.01
KL24-05	39.7	43	0.0148		148	0.21	1.2	218	113	17	7	2	2	1.1	1.3	211	0.01
KL24-05	43	45.8	0.0076		76	0.06	0.7	660	640	7	5	2	2	1.5	1.5	66	0.01
KL24-05	45.8	47.5	0.01		100	0.1	0.5	500	254	19	7	1	1	0.9	0.7	20	0.01
KL24-05	47.5	49.7	0.0139		139	0.04	0.1	365	270	23	7	0.01	1	0.9	0.0	30	0.01
KL24-05	49.7	52	0.0052		52	0.1	1	242	210	49	6	2	1	0.9	1.1	110	0.01
KL24-05	52	55	0.0075		75	0.03	0.1	185	257	5	6	1	1	0.8	1.2	9	0.01
KL24-05	55	58	0.01		100	0.03	0.1	350	350	8	4	2	2	0.9	1.7	11	0.01
KL24-05	58	61.1	0.0074		74	0.02	0.1	310	181	8	6	1	1	0.8	0.0	8	0.01
KL24-05	61.1	62.5	0.0045		45	0.03	0.1	307	113	29	3	0.01	1	2.2	0.0	12	0.01
KL24-05	62.5	65.5	0.005		50	0.02	0.1	149	180	26	1	0.01	1	3.1	0.0	14	0.01
KL24-05	65.5	68	0.0094		94	0.03	1.4	421	337	34	6	2	1	3.5	0.0	19	0.01
KL24-05	68	71.3	0.021		210	0.1	3.3	337	570	45	20	13	1	3	3.0	25	0.01
KL24-05	71.3	74	0.0092		92	0.04	3.2	267	1750	28	1	1	1	1.7	2.8	22	0.01
KL24-05	74	77.3	0.0051		51	0.02	4.5	460	1310	25	3	0.01	1	2.6	0.7	15	0.01
KL24-05	77.3	80.3	0.0046		46	0.01	9.8	1390	3400	14	5	0.01	1	4.3	1.3	18	0.01
KL24-05	80.3	83.5	0.0078		78	0.03	2.4	287	640	10	2	0.01	1	1.5	0.0	16	0.01
KL24-05	83.5	85.5	0.0024		24	0.04	2.1	297	730	6	5	1	1	1.3	0.0	26	0.01
KL24-05	85.5	88	0.0053		53	0.05	3.8	920	1640	12	5	2	1	2.4	2.9	26	0.01
KL24-05	88	90.7	0.0114		114	0.13	24.5	361	1630	50	4	2	1	6	2.7	31	0.12
KL24-05	90.7	93	0.0047		47	0.05	9.7	231	550	22	8	1	1	2.2	1.3	26	0.01
KL24-05	93	97	0.0044		44	0.09	8.6	470	1020	20	7	1	1	0.8	0.8	25	0.01
KL24-05	97	101	0.002		20	0.04	5.7	590	1040	19	12	0.01	1	1.8	1.2	21	0.01
KL24-05	101	104.5	0.0082		82	0.05	4	340	750	15	9	2	1	1.5	2.3	22	0.01
KL24-05	104.5	106.2	0.0025		25	0.04	8.1	450	530	11	22	0.01	1	1	0.0	12	0.01
KL24-05	106.2	109	0.0017		17	0.04	12.8	200	412	6	11	0.01	1	0.6	0.0	11	0.01
KL24-05	109	112	0.0029		29	0.02	7.3	308	880	6	12	0.01	1	1.5	0.0	15	0.01
KL24-05	112	115	0.001		10	0.01	1.8	184	230	4	6	0.01	1	0.5	0.0	13	0.01
KL24-05	115	118	0.0014		14	0.01	2.3	195	720	6	4	0.01	1	1	0.0	13	0.01
KL24-05	118	121	0.0052		52	0.01	3.6	312	1200	7	10	0.01	1	3	0.8	12	0.01
KL24-05	121	123.5	0.0042		42	0.01	2.1	170	540	21	22	0.01	1	1.1	0.9	18	0.01
KL24-05	123.5	126	0.0098		98	0.02	4.2	329	1050	16	20	0.01	1	2.1	3.4	24	0.01
KL24-05	126	129	0.0234		234	0.01	4.7	200	1240	25	60	1	1	2.9	2.9	25	0.01
KL24-05	129	132	0.0094		94	0.01	4.7	237	2590	15	71	2	1	3.3	2.3	21	0.01
KL24-05	132	134.4	0.0029		29	0.01	2.8	440	830	5	7	0.01	1	1	1.4	16	0.01
KL24-05	134.4	137.5	0.0033		33	0.01	4.3	610	1370	9	7	1	1	2	1.1	12	0.01
KL24-05	137.5	140.5	0.0024		24	0.01	1.8	180	358	7	6	0.01	1	1.2	1.9	16	0.01
KL24-05	140.5	143.5	0.0019		19	0.01	0.9	145	265	7	6	0.01	1	0.8	0.9	13	0.01
KL24-05	143.5	146	0.0019		19	0.01	0.8	381	163	5	5	0.01	1	0.8	0.7	13	0.01
KL24-05	146	149.2	0.0032		32	0.01	0.1	143	136	3	1	0.01	1	0.6	0.7	17	0.01
KL24-05	149.2	152.4	0.0023		23	0.01	2.6	1380	1270	15	3	0.01	1	2.9	1.7	17	0.01
KL24-05	152.4	155.5	0.0189		189	0.02	1.1	271	410	21	9	0.01	1	1.5	1.5	16	0.01
KL24-05	155.5	158.5	0.004		40	0.01	0.6	70	187	14	12	0.01	1	0.8	1.1	26	0.01
KL24-05	158.5	161.5	0.02		200	0.14	31.9	13100	14100	27	85	0.01	1	38	24.2	21	0.18
KL24-05	161.5	164.5	0.0052		52	0.04	6.2	1540	3870	11	16	3	1	3.4	2.6	16	0.01
KL24-05	164.5	167.5	0.0043		43	0.06	5.2	1680	4500	11	55	4	1	3.1	2.6	13	0.01
KL24-05	167.5	170	0.0035		35	0.02	2	930	1800	5	77	1	1	2.2	2.6	16	0.01
KL24-05	170	173.5	0.0034		34	0.02	0.9	450	780	6	62	1	1	0.8	1.4	15	0.01
KL24-05	173.5	176.5	0.0018		18	0.01	0.1	143	380	3	13	0.01	1	0.3	1.7	19	0.01
KL24-05	176.5	179.5	0.0046		46	0.01	0.1	141	272	4	13	0.01	1	0.8	2.1	20	0.01
KL24-05	179.5	182.5	0.0023		23	0.01	0.5	283	295	4	21	0.01	1	0.6	1.4	14	0.01
KL24-05	182.5	185.5	0.0038		38	0.01	0.6	324	387	8	17	0.01	1	0.5	1.1	19	0.01
KL24-05	185.5	188.5	0.017		170	0.11	6.9	4770	1790	19	18	176	2	2.3	64.0	23	0.01
KL24-05	188.5	191.5	0.0128		128	0.24	5.8	3030	1250	35	7	34	1	2.6	43.0	18	0.01
KL24-05	191.5	194	0.01		100	0.02	1.4	1220	950	14	22	4	1	1.8	3.0	11	0.01
KL24-05	194	196	0.0126		126	0.14	12.7	470	1850	56	1180	248	1	2.3	32.4	66	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL24-05	196	199	0.085	850	0.45	12.5	3350	6900	92	3750	186	3	8	26.6	60	0.16
KL24-05	199	202	0.396	3960	0.81	14	6000	3260	58	860	77	10	3.7	8.8	60	0.15
KL24-05	202	204.8	0.13	1300	0.56	3.2	2700	362	110	71	11	8	4.9	8.1	19	0.01
KL24-05	204.8	206.4	0.27	2700	1	3.9	23900	127	31	63	540	12	0.4	76.8	24	0.01
KL24-05	206.4	209.5	0.67	6700	3	11	40000	95	47	280	1440	22	1.7	131.0	24	0.01
KL24-05	209.5	212.5	0.69	6900	2.52	8	1320	62	22	680	1560	37	1.1	140.0	31	0.01
KL24-05	212.5	215.7	0.43	4300	1.91	2.7	137	95	33	1360	350	15	0.01	10.1	37	0.01
KL24-05	215.7	217.2	1.47	14700	3.79	12	371	117	35	2525	218	57	0.01	16.8	66	0.01
KL24-05	217.2	221.2	0.7	7000	1.89	4.2	417	86	56	4750	88	19	0.9	23.1	57	0.01
KL24-05	221.2	222.6	0.337	3370	1.41	2.3	479	49	26	179	110	6	0.2	6.2	28	0.01
KL24-05	222.6	223.9	1.01	10100	2.44	6.8	13100	45	43	400	248	22	0.9	24.0	54	0.01
KL24-05	223.9	226.6	0.398	3980	1.2	1.6	5200	22	13	19	51	12	0.3	9.3	18	0.01
KL24-05	226.6	229.6	0.371	3710	0.94	1.4	575	18	12	145	11	8	0.01	7.2	33	0.01
KL24-05	229.6	232	1.08	10800	1.5	2	291	27	32	208	2	8	0.01	6.2	35	0.01
KL24-05	232	235	0.133	1330	0.41	1.3	91	44	37	2800	11	4	0.7	7.4	25	0.01
KL24-05	235	238	0.097	970	0.4	1	50	26	31	2975	7	3	0.8	6.5	55	0.01
KL24-05	238	239.5	1.2	12000	2.52	8.2	910	41	27	130	15	18	2.2	22.0	69	0.01
KL24-05	239.5	242.5	1.26	12600	5.83	25.2	43800	2330	24	198	156	14	1	15.4	44	0.01
KL24-05	242.5	244.7	0.49	4900	2.43	4.3	9600	162	20	24	36	5	1	27.0	26	0.01
KL24-05	244.7	247	1.31	13100	5.54	7.4	2800	306	10	50	108	6	1.9	31.5	25	0.01
KL24-05	247	250	0.389	3890	1.35	1.5	3060	48	7	65	14	9	0.5	39.4	53	0.01
KL24-05	250	253	0.41	4100	0.48	0.8	158	17	4	78	6	41	0.3	37.5	35	0.01
KL24-05	253	256	0.394	3940	0.59	0.9	94	12	6	174	5	58	0.2	35.0	57	0.01
KL24-05	256	259.7	1.08	10800	1.34	2.8	234	12	6	65	5	31	0.4	47.0	23	0.01
KL24-05	259.7	262	3.63	36300	4.85	6.3	520	153	9	165	2	68	0.2	40.0	45	0.01
KL24-05	262	264	3.05	30500	3.25	5.4	182	13	2	137	1	51	0.01	28.0	57	0.01
KL24-05	264	265	1.69	16900	1.26	3.6	113	10	2	206	1	45	0.01	7.0	27	0.01
KL24-05	265	267	2.54	25400	1.61	2.7	300	25	4	160	0.01	43	0.2	16.5	87	0.01
KL24-05	267	269.5	2.61	26100	1.95	4	146	15	3	47	1	55	0.3	21.0	61	0.01
KL24-05	269.5	272.5	3.64	36400	2.33	17.3	2140	600	29	570	1	55	2.7	15.0	48	0.29
KL24-05	272.5	275	1.68	16800	1.03	17.5	1140	1200	510	640	1	46	188	15.5	93	0.39
KL24-05	275	277	2.79	27900	2.11	5.7	322	106	54	434	2	38	5.5	23.5	118	0.01
KL24-05	277	280	3.01	30100	1.41	2.6	104	28	14	288	0.01	37	2.9	17.5	143	0.01
KL24-05	280	283	3.82	38200	3.42	27.8	6900	5010	1120	560	1	31	720	30.0	169	1.85
KL24-05	283	286	3.8	38000	2.59	8.4	247	103	280	750	1	54	18	29.0	161	0.01
KL24-05	286	289	7.05	70500	3.68	13.9	430	164	1250	450	1	80	38	52.5	157	0.01
KL24-05	289	292.1	5.31	53100	2	18.2	1140	610	2000	1460	1	46	40	20.9	172	0.57
KL24-05	292.1	295	1.56	15600	0.39	4	217	180	220	1220	4	13	3.5	11.5	90	0.17
KL24-05	295	298	0.67	6700	0.14	1.9	153	188	290	780	1	7	2.1	9.3	127	0.1
KL24-05	298	301	0.71	7100	0.27	2.8	288	312	410	1210	4	10	9.2	9.3	122	0.11
KL24-05	301	303	1.55	15500	1.17	4.1	427	385	39	1400	0.01	17	2.7	18.5	145	0.17
KL24-05	303	305	3.56	35600	3.19	7.2	224	21	4	470	0.01	110	0.2	16.0	98	0.01
KL24-05	305	308.6	1.46	14600	2.24	8	241	18	5	62	3	31	0.5	12.3	53	0.01
KL24-05	308.6	311.5	1.47	14700	3.96	9.4	376	14	6	6	4	60	0.3	22.8	86	0.01
KL24-05	311.5	312.5	2.38	23800	6.24	18.1	660	15	13	10	3	67	0.4	21.0	63	0.01
KL24-05	312.5	314.8	2.36	23600	4.36	15.4	640	18	3	19	3	136	0.3	24.5	59	0.01
KL24-05	314.8	316.9	4.04	40400	5.18	19.3	3700	20	3	530	2	105	0.01	28.0	93	0.01
KL24-05	316.9	319.8	2.25	22500	3.58	10.2	15500	14	7	197	4	197	0.3	46.5	84	0.01
KL24-05	319.8	322.1	3	30000	3.04	13.7	6300	12	2	89	4	188	0.01	37.5	82	0.01
KL24-05	322.1	325	1.63	16300	2.42	13.4	2200	11	7	95	2	64	0.2	17.5	47	0.01
KL24-05	325	326.1	0.97	9700	0.72	4.9	261	10	7	23	1	61	0.01	7.5	53	0.01
KL24-05	326.1	327.7	7.56	75600	6.35	35	34300	14	3	31	5	144	0.01	22.5	59	0.01
KL24-05	327.7	329	2.98	29800	2.75	17	20700	12	2	167	46	60	0.01	20.5	55	0.01
KL24-05	329	330.4	1.1	11000	0.75	5.2	650	11	15	48	10	80	0.01	19.5	83	0.01
KL24-05	330.4	331.8	1.08	10800	0.85	6.1	415	13	13	45	2	78	0.01	16.5	82	0.01
KL24-05	331.8	332.5	14.1	141000	12.4	122	740	12	15	16	62	179	0.01	47.5	57	0.01
KL24-05	332.5	334	1.58	15800	1.28	11.8	187	14	9	57	9	67	0.2	23.3	62	0.01
KL24-05	334	335.9	3.37	33700	3.62	32.5	610	41	20	328	80	98	0.2	34.0	86	0.01
KL24-05	335.9	337	1.08	10800	1.01	9.3	376	18	32	134	38	59	0.5	103.0	108	0.01
KL24-05	337	339.3	2.69	26900	1.48	11.8	7000	26	50	21	76	18	2.8	68.0	162	0.01
KL24-05	339.3	341.5	0.59	5900	0.65	2.6	770	38	39	3	8	2	1.8	3.6	23	0.01
KL24-05	341.5	344.5	0.0267	267	0.19	1.5	710	2700	43	5	1	1	3.8	1.6	25	0.01
KL24-05	344.5	347.5	0.0247	247	0.05	0.1	164	29	15	4	4	1	0.5	0.9	14	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL24-05	347.5	350.5	0.015		150	0.06	0.1	124	50	23	2	0.01	1	0.7	0.8	18	0.01
KL24-05	350.5	353.5	0.0124		124	0.1	0.1	153	166	32	3	2	2	0.8	2.0	25	0.01
KL24-05	353.5	356.5	0.22		2200	0.25	0.5	116	50	50	29	2	3	1.6	2.4	25	0.01
KL24-05	356.5	359.5	0.0154		154	0.06	0.1	106	22	26	4	1	1	1.3	0.5	19	0.01
KL24-05	359.5	362.5	0.0115		115	0.04	0.1	65	18	12	2	0.01	1	0.4	0.0	17	0.01
KL24-05	362.5	365.5	0.0092		92	0.04	0.1	64	98	15	2	2	1	0.6	1.3	16	0.01
KL24-05	365.5	368.5	0.0085		85	0.1	0.1	100	30	40	2	1	2	1.4	1.0	22	0.01
KL24-05	368.5	371.5	0.0071		71	0.23	0.1	245	39	3	3	0.01	2	1.4	1.5	35	0.01
KL24-05	371.5	373	0.0056		56	0.02	0.1	39	24	10	2	0.01	1	0.2	0.0	11	0.01
KL24-06	0	3	0.0074		74	0.01	0.1	69	31	5	1	0.01	1	0.2	1.2	23	0.01
KL24-06	3	5	0.0023		23	0.03	0.1	156	48	7	1	0.01	1	0.8	1.1	24	0.01
KL24-06	5	8	0.002		20	0.02	0.1	104	46	17	3	0.01	1	1.3	1.9	22	0.01
KL24-06	8	11	0.0026		26	0.01	0.1	44	28	7	1	0.01	1	0.9	1.0	34	0.01
KL24-06	11	14	0.0035		35	0.01	0.1	50	22	4	1	0.01	1	0.4	1.5	33	0.01
KL24-06	14	17	0.0042		42	0.01	0.1	32	27	7	1	0.01	1	0.4	1.0	20	0.01
KL24-06	17	20	0.0016		16	0.01	0.1	130	75	8	1	0.01	1	0.4	1.9	32	0.01
KL24-06	20	23	0.0015		15	0.01	0.1	77	35	8	1	0.01	1	0.8	1.8	30	0.01
KL24-06	23	26	0.0042		42	0.01	0.1	55	66	10	1	0.01	1	0.5	2.5	28	0.01
KL24-06	26	29	0.007		70	0.02	0.7	39	348	11	1	0.01	1	1.6	7.9	58	0.01
KL24-06	29	32	0.0195		195	0.01	0.8	34	91	19	2	0.01	2	0.9	2.9	87	0.01
KL24-06	32	34.8	0.029		290	0.11	15.2	46	5010	21	15	0.01	5	5	92.1	110	0.01
KL24-06	34.8	35.4	0.0274		274	0.04	0.6	32	97	32	14	0.01	7	1.3	4.6	114	0.01
KL24-06	35.4	36.2	0.0175		175	0.14	0.7	79	211	35	6	0.01	9	1.7	3.6	63	0.01
KL24-06	36.2	38	0.023		230	0.14	10.2	2500	1600	33	17	13	5	3	25.0	117	0.01
KL24-06	38	41	0.0129		129	0.15	16.5	3700	15200	35	17	7	2	12.6	54.0	35	0.01
KL24-06	41	44	0.0225		225	0.17	2.5	1440	600	27	28	1	1	2.4	3.9	56	0.01
KL24-06	44	47	0.0186		186	0.15	1.5	82	54	21	26	1	2	2	1.0	59	0.01
KL24-06	47	50	0.0149		149	0.05	0.1	42	32	10	13	0.01	1	1	1.3	38	0.01
KL24-06	50	52.2	0.0395		395	0.07	0.6	75	46	25	5	0.01	2	1.4	0.6	42	0.01
KL24-06	52.2	54	0.0367		367	0.15	1	169	128	42	7	3	3	2.7	2.4	38	0.01
KL24-06	54	56	0.0183		183	0.06	0.1	59	45	19	7	1	1	0.9	0.8	39	0.01
KL24-06	56	57.2	0.02		200	0.07	0.1	77	39	10	13	0.01	1	1.8	0.5	25	0.01
KL24-06	57.2	59	0.0214		214	0.1	1.2	160	200	14	7	1	2	1.6	1.4	35	0.01
KL24-06	59	62	0.0173		173	0.11	0.1	372	46	7	4	1	2	0.9	0.8	30	0.01
KL24-06	62	64	0.02		200	0.24	0.1	149	71	22	1	2	2	3	1.9	30	0.01
KL24-06	64	65	0.0154		154	0.27	0.7	163	105	23	1	3	1	2.4	1.9	34	0.01
KL24-06	65	68	0.01		100	0.43	1.2	306	195	34	3	3	2	3.3	2.6	20	0.01
KL24-06	68	77	0.0293		293	0.43	2.8	480	560	160	7	2	2	7.6	3.0	18	0.01
KL24-06	77	80	0.049		490	0.42	1.5	297	354	190	18	1	1	14.5	2.6	23	0.01
KL24-06	80	83	0.38		3800	0.67	9.7	1640	2250	1500	52	7	9	38	4.2	41	0.22
KL24-06	83	84.5	0.057		570	0.43	7.5	302	330	260	30	2	2	12	3.7	36	0.19
KL24-06	84.5	86	0.063		630	0.23	5.2	670	1100	300	18	3	2	5.2	3.2	29	0.01
KL24-06	86	89	0.0116		116	0.08	3.7	109	700	45	4	1	3	1.9	1.8	24	0.01
KL24-06	89	91.5	0.0132		132	0.9	8.9	397	1000	57	22	3	2	7.6	2.2	35	0.01
KL24-06	91.5	93.5	0.0066		66	0.14	3	219	600	17	14	0.01	1	2.4	2.0	16	0.01
KL24-06	93.5	95	0.0051		51	0.08	2.2	172	680	25	16	1	1	2.4	2.9	22	0.01
KL24-06	95	99.7	0.0064		64	0.46	7.8	273	1900	47	6	3	1	4.1	3.9	23	0.01
KL24-06	99.7	102	0.0104		104	0.05	2.6	112	780	18	9	2	1	3.9	4.2	23	0.01
KL24-06	102	107	0.0047		47	0.14	5.1	900	1870	22	3	2	1	6	4.5	30	0.01
KL24-06	107	111.5	0.0018		18	0.06	2.4	179	490	9	10	1	2	0.9	0.6	24	0.01
KL24-06	111.5	113	0.003		30	0.03	4	245	950	6	21	5	1	0.9	2.0	27	0.01
KL24-06	113	115.7	0.002		20	0.02	1.6	178	610	6	4	2	1	2	1.2	28	0.01
KL24-06	115.7	118.5	0.0043		43	0.02	3.6	158	660	12	14	1	1	1.6	1.4	12	0.01
KL24-06	118.5	121.5	0.0035		35	0.01	2.3	341	348	4	5	0.01	1	0.9	1.0	13	0.01
KL24-06	121.5	124	0.057		570	0.05	11.4	1330	3350	120	18	5	1	9	1.8	13	0.01
KL24-06	124	127	0.0032		32	0.02	2	182	800	4	11	0.01	2	2	1.1	16	0.01
KL24-06	127	130	0.0017		17	0.01	1.8	154	600	5	16	1	1	1	0.7	13	0.01
KL24-06	130	133	0.0072		72	0.06	12.5	4400	8000	8	1	0.01	1	10.1	2.8	14	0.01
KL24-06	133	136	0.0043		43	0.02	8.8	1480	5020	9	3	0.01	1	6.9	2.9	11	0.01
KL24-06	136	140.5	0.002		20	0.02	2.2	165	600	13	5	0.01	1	1.6	1.3	16	0.01
KL24-06	140.5	143.2	0.0033		33	0.02	8.1	876	3900	10	5	0.01	2	7.5	2.0	14	0.01
KL24-06	143.2	146	0.0054		54	0.01	2.6	73	308	9	1	0.01	1	1.5	1.0	14	0.01
KL24-06	146	148	0.0101		101	0.01	4.6	43	154	31	1	2	1	1.4	0.5	11	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL24-06	148	151	0.0137		137	0.02	7.5	192	600	31	22	3	2	2.9	1.3	21	0.01
KL24-06	151	154	0.0055		55	0.02	3.4	94	520	8	3	2	1	1.2	0.8	14	0.01
KL24-06	154	157	0.0036		36	0.01	2.1	109	301	4	8	2	1	1.1	1.1	18	0.01
KL24-06	157	160	0.0051		51	0.02	2.4	233	560	7	3	1	1	1.4	1.1	13	0.01
KL24-06	160	163	0.0085		85	0.03	14.2	1950	1630	19	5	0.01	1	6.7	3.1	17	0.01
KL24-06	163	165.5	0.0042		42	0.01	1.2	66	169	7	4	0.01	1	1	0.8	14	0.01
KL24-06	165.5	167	0.0032		32	0.01	1.1	92	118	22	6	0.01	2	1.2	1.0	15	0.01
KL24-06	167	169	0.027		270	0.01	0.9	91	49	12	6	0.01	3	0.5	0.7	22	0.01
KL24-06	169	171.5	0.0012		12	0.02	1.2	103	216	3	3	0.01	2	0.5	0.8	14	0.01
KL24-06	171.5	173.5	0.0012		12	0.01	0.7	36	67	4	1	0.01	1	0.3	0.6	12	0.01
KL24-06	173.5	175.5	0.0113		113	0.06	1	71	98	7	7	0.01	1	0.9	2.0	15	0.01
KL24-06	175.5	177.5	0.0049		49	0.03	2.3	580	1140	6	3	0.01	1	1.3	1.2	14	0.01
KL24-06	177.5	180.5	0.0145		145	0.02	1.4	147	388	17	7	0.01	2	1.3	0.6	19	0.01
KL24-06	180.5	183.6	0.0185		185	0.24	12.8	4610	5800	32	59	0.01	2	11.4	3.6	21	0.25
KL24-06	183.6	186.7	0.0031		31	0.09	1.9	329	600	15	4	0.01	1	1.5	1.7	15	0.01
KL24-06	186.7	189.8	0.0063		63	0.16	6.3	6900	6800	25	29	0.01	2	5.7	7.2	18	0.01
KL24-06	189.8	192.8	0.0035		35	0.08	4.2	2100	5500	7	18	1	2	3	2.5	18	0.01
KL24-06	192.8	195.8	0.0015		15	0.05	1.3	166	700	11	23	0.01	1	1	2.7	19	0.01
KL24-06	195.8	198.8	0.0011		11	0.03	0.8	130	376	9	4	0.01	1	0.7	2.8	15	0.01
KL24-06	198.8	201	0.0016		16	0.02	0.8	127	600	9	7	0.01	2	0.3	1.5	11	0.01
KL24-06	201	203.3	0.0027		27	0.05	4	3960	3720	16	9	1	1	3.2	2.3	13	0.01
KL24-06	203.3	205	0.0017		17	0.02	0.9	223	600	7	6	0.01	1	0.3	0.6	15	0.01
KL24-06	205	208	0.0028		28	0.06	0.8	323	380	13	13	1	1	0.4	1.0	20	0.1
KL24-06	208	211	0.0144		144	0.22	8.5	1970	2330	33	126	28	3	1.7	3.7	35	0.48
KL24-06	211	214	0.0044		44	0.12	2	570	700	18	18	2	2	1.2	1.9	18	0.01
KL24-06	214	217	0.0255		255	1.18	9	4500	5200	50	24	16	2	8.6	8.2	33	0.85
KL24-06	217	220	0.0503		503	0.49	5.1	3030	940	72	960	14	3	5.6	7.0	51	0.34
KL24-06	220	223	0.08		800	0.21	1.5	354	117	41	590	12	3	4.3	5.7	116	0.01
KL24-06	223	226	0.063		630	0.38	2.3	640	183	81	810	40	5	7.3	5.2	105	0.01
KL24-06	226	229.2	0.071		710	0.25	1.5	1490	106	33	452	16	4	4.4	4.3	78	0.13
KL24-06	229.2	231.8	0.057		570	0.27	1.3	660	132	53	275	14	1	2.9	4.3	81	0.01
KL24-06	231.8	233.1	0.124		1240	0.28	3.6	11700	440	210	345	16	8	7.9	13.0	70	0.29
KL24-06	233.1	234.9	0.125		1250	0.16	3.1	2300	840	350	20	6	1	12	3.1	23	0.26
KL24-06	234.9	238	0.34		3400	0.9	25.1	21800	5900	900	1667	90	10	32	16.6	63	2.13
KL24-06	238	241	0.348		3480	0.47	8.1	2310	910	260	1100	39	13	4.8	7.2	85	0.62
KL24-06	241	244	0.422		4220	1.04	34	5900	3000	580	4200	460	13	5.3	14.3	100	1.28
KL24-06	244	247	0.45		4500	1.59	155	48500	54400	400	380	470	14	5.9	50.0	107	5.74
KL24-06	247	250	0.27		2700	1.23	38	9900	8300	450	1720	237	9	4.2	24.4	84	1.65
KL24-06	250	253	0.33		3300	1.85	4.9	5100	540	200	900	66	6	2.4	7.3	80	1.17
KL24-06	253	256	0.068		680	1.04	5.6	1000	312	110	1590	63	5	0.9	19.3	51	0.96
KL24-06	256	257	0.095		950	1.26	6.2	1150	315	110	400	113	5	0.6	13.0	51	0.85
KL24-06	257	259	5.07		50700	4.65	62	247000	1560	240	380	550	194	2.1	66.9	50	1.85
KL24-06	259	262	0.79		7900	3.41	18.5	127000	440	310	45	120	91	2.8	62.5	91	0.72
KL24-06	262	265	0.178		1780	0.65	7.5	4430	600	170	42	46	8	1.4	10.8	26	0.3
KL24-06	265	268	0.21		2100	1.2	26.5	7900	6400	180	32	131	18	2.5	17.8	31	0.61
KL24-06	268	271	2.8		28000	4.53	86	51700	7200	250	102	348	88	1.8	29.5	38	0.23
KL24-06	271	274	0.85		8500	2.44	24.3	21900	1130	280	180	122	38	0.9	12.8	33	0.1
KL24-06	274	277	0.183		1830	1.1	11.7	3600	830	120	50	54	15	0.4	9.0	24	0.01
KL24-06	277	280	0.233		2330	0.94	27.2	6000	870	140	29	90	4	0.5	15.5	19	0.01
KL24-06	280	283	0.5		5000	1.72	17.1	16900	480	230	64	144	7	0.7	50.5	32	0.2
KL24-06	283	285	0.156		1560	0.62	3.5	2070	172	140	35	59	14	0.8	12.5	30	0.1
KL24-06	285	288.1	0.37		3700	2	3	9000	60	140	87	93	39	3.2	61.8	42	0.11
KL24-06	288.1	291.2	1.59		15900	3.81	15	7300	66	210	32	204	17	0.9	137.0	47	0.29
KL24-06	291.2	294.3	0.65		6500	1.84	11.2	6800	720	450	74	73	9	1.4	16.8	44	1.5
KL24-06	294.3	295.5	0.58		5800	1.13	10.4	6100	1630	170	34	42	17	2.3	7.6	31	0.7
KL24-06	295.5	297.5	0.044		440	0.24	2.7	1910	630	38	22	17	1	1	3.0	17	0.11
KL24-06	297.5	300.6	0.65		6500	0.96	5.9	2100	128	170	32	29	17	1.8	6.0	31	0.12
KL24-06	300.6	303.7	0.059		590	0.51	5.6	5900	860	90	207	58	3	0.8	6.3	26	0.25
KL24-06	303.7	306.8	0.01		100	0.13	1.7	2160	285	21	56	7	4	0.2	3.8	16	0.01
KL24-06	306.8	308	0.0038		38	0.06	0.1	236	67	12	25	2	1	0.01	1.3	14	0.01
KL24-06	308	311	0.0185		185	0.13	2.1	3320	950	23	133	28	1	0.4	8.0	17	0.11
KL24-06	311	313	0.0203		203	0.21	4.6	9000	6900	120	36	4	1	2.4	3.3	16	0.1
KL24-06	313	316	0.142		1420	0.6	9.3	12500	3400	170	198	40	3	3.3	8.5	32	0.26

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL24-06	316	319	0.059		590	0.14	1.1	880	182	34	11	1	1	0.4	1.8	16	0.01
KL24-06	319	321	0.016		160	0.06	0.1	265	46	21	3	0.01	1	0.2	1.5	14	0.01
KL24-06	321	324	0.041		410	0.14	2.9	1140	368	50	17	5	1	1.1	2.3	16	0.14
KL24-06	324	327.1	0.0398		398	0.24	47	29200	23300	88	15	4	1	42	25.3	16	0.17
KL24-06	327.1	330.2	0.051		510	0.15	2.6	1880	800	28	25	4	2	0.5	2.8	16	0.01
KL24-06	330.2	333.3	0.0211		211	0.41	2.3	670	420	27	54	25	1	0.3	3.8	16	0.01
KL24-06	333.3	336.4	0.081		810	0.11	1.6	630	270	43	15	3	1	0.01	3.0	12	0.1
KL24-06	336.4	339.4	0.0139		139	0.06	2.7	820	610	20	14	7	1	0.3	3.8	10	0.01
KL24-06	339.4	342.4	0.0283		283	0.06	1	670	189	32	13	2	2	0.6	2.8	14	0.01
KL24-06	342.4	345.4	0.0079		79	0.16	1.1	850	680	17	9	3	1	1.1	4.0	13	0.1
KL24-06	345.4	348.4	0.0397		397	0.17	1.9	810	388	56	25	2	1	1.7	3.3	21	0.01
KL24-06	348.4	351.8	0.0071		71	0.06	2.4	550	303	13	10	2	1	0.9	1.2	16	0.01
KL24-06	351.8	354.9	0.0135		135	0.07	3.6	1930	810	25	23	5	1	1.1	2.3	14	0.01
KL24-06	354.9	358	0.0215		215	0.36	2	1120	590	37	29	7	3	1.3	6.6	29	0.01
KL24-06	358	360.6	0.0071		71	0.3	1.4	730	510	40	17	3	2	1	1.6	18	0.01
KL24-06	360.6	365	0.014		140	0.07	0.6	470	195	9	10	2	1	0.7	1.8	10	0.01
KL24-06	365	367.5	0.0176		176	0.06	0.5	305	56	45	20	0.01	1	2.3	3.0	11	0.01
KL24-06	367.5	370	0.0061		61	0.02	0.1	213	97	7	11	1	1	0.2	0.5	10	0.01
KL24-07	0	3	0.0056		56	0.02	0.1	67	28	6	1	0.01	1	0.3	2.3	23	0.01
KL24-07	3	4.5	0.004		40	0.01	0.1	40	24	3	2	0.01	1	0.3	0.8	20	0.01
KL24-07	4.5	8	0.003		30	0.01	0.1	39	23	5	1	0.01	1	0.01	1.1	21	0.01
KL24-07	8	11	0.0067		67	0.03	4	695	391	26	1	0.01	1	3.1	1.9	19	0.01
KL24-07	11	14	0.0018		18	0.01	0.1	45	37	9	1	0.01	1	0.8	1.7	33	0.01
KL24-07	14	16.5	0.0022		22	0.01	0.1	85	51	7	1	0.01	1	0.5	1.0	32	0.01
KL24-07	16.5	18	0.0019		19	0.01	0.1	53	78	9	1	0.01	1	0.01	0.0	41	0.01
KL24-07	18	21	0.0026		26	0.01	0.1	64	24	10	1	0.01	1	0.3	1.4	26	0.01
KL24-07	21	24	0.0024		24	0.01	0.1	38	20	12	1	0.01	1	0.3	1.1	27	0.01
KL24-07	24	27	0.0013		13	0.01	0.1	36	28	7	1	0.01	1	0.01	0.9	35	0.01
KL24-07	27	30	0.0012		12	0.01	0.1	30	34	5	1	0.01	1	0.3	1.2	36	0.01
KL24-07	30	33	0.0069		69	0.01	0.1	40	24	4	1	0.01	1	0.3	1.8	22	0.01
KL24-07	33	36	0.0024		24	0.01	0.1	40	24	2	1	0.01	1	0.01	1.2	24	0.01
KL24-07	36	39	0.0098		98	0.03	0.1	51	108	14	5	0.01	1	1.1	2.0	61	0.01
KL24-07	39	41.5	0.0174		174	0.01	0.1	54	24	8	5	0.01	1	0.9	0.7	73	0.01
KL24-07	41.5	43.5	0.0262		262	0.04	0.1	64	38	26	9	0.01	1	1.6	1.7	106	0.01
KL24-07	43.5	46.2	0.0116		116	0.01	0.1	24	30	15	5	0.01	2	0.9	2.1	90	0.01
KL24-07	46.2	48.55	0.0385		385	0.04	0.1	37	38	25	14	0.01	6	1.5	5.1	138	0.01
KL24-07	48.55	51	0.0314		314	0.1	11.5	1130	980	52	18	5	2	4.6	12.1	78	0.01
KL24-07	51	54	0.0048		48	0.13	4.6	161	317	11	9	1	1	2.4	2.8	14	0.01
KL24-07	54	56	0.0149		149	0.38	7.9	720	2780	56	26	37	1	5.6	31.0	30	0.01
KL24-07	56	57	0.0237		237	0.09	2.7	2100	3260	36	16	5	1	2.3	5.9	47	0.01
KL24-07	57	59.45	0.017		170	0.15	1.7	133	241	30	13	4	1	1.2	8.0	31	0.1
KL24-07	59.45	61.3	0.0096		96	0.13	1.8	184	225	43	8	5	1	2.8	4.6	40	0.01
KL24-07	61.3	64.3	0.012		120	0.15	1.1	80	101	34	42	4	1	2	2.5	42	0.01
KL24-07	64.3	67	0.0125		125	0.06	0.1	58	56	8	26	2	1	0.8	0.0	29	0.01
KL24-07	67	69	0.0103		103	0.16	0.1	51	31	15	8	2	1	1.4	0.8	23	0.01
KL24-07	69	71.5	0.0115		115	0.1	0.1	62	41	19	11	1	1	1.2	0.5	27	0.01
KL24-07	71.5	72.8	0.0134		134	0.06	0.1	60	75	19	10	1	1	1.3	1.2	30	0.01
KL24-07	72.8	75.5	0.0157		157	0.03	0.1	42	38	5	6	0.01	1	0.4	0.5	26	0.01
KL24-07	75.5	77.25	0.0063		63	0.06	0.1	86	43	12	8	0.01	1	1.3	1.1	11	0.01
KL24-07	77.25	78.75	0.0096		96	0.02	0.1	68	50	3	5	0.01	1	0.5	0.7	18	0.01
KL24-07	78.75	81	0.0138		138	0.07	0.1	57	30	4	9	0.01	1	0.5	5.0	31	0.01
KL24-07	81	84	0.0061		61	0.04	0.1	70	38	6	11	0.01	1	0.9	1.1	15	0.01
KL24-07	84	86.8	0.0069		69	0.02	0.1	48	27	4	10	0.01	1	0.9	0.0	13	0.01
KL24-07	86.8	89.9	0.0101		101	0.05	0.1	50	40	5	7	1	1	0.7	0.0	13	0.01
KL24-07	89.9	92.9	0.0078		78	0.08	0.1	105	160	16	8	0.01	1	1.6	0.8	9	0.01
KL24-07	92.9	93.9	0.011		110	0.06	0.1	114	184	16	9	0.01	1	2.2	0.7	11	0.01
KL24-07	93.9	96	0.0059		59	0.03	0.1	76	284	14	9	0.01	1	2.7	0.0	9	0.01
KL24-07	96	99	0.0025		25	0.06	0.7	67	187	15	14	0.01	1	2.5	0.0	33	0.01
KL24-07	99	100.75	0.0054		54	0.02	0.1	56	300	13	13	0.01	1	3.1	0.0	80	0.01
KL24-07	100.75	102	0.0022		22	0.05	0.1	51	164	4	7	0.01	1	1.5	0.0	30	0.01
KL24-07	102	105	0.0014		14	0.13	0.1	75	120	6	3	0.01	1	0.9	0.7	38	0.01
KL24-07	105	108	0.0021		21	0.11	0.1	50	70	5	3	0.01	1	0.7	1.2	26	0.01
KL24-07	108	111	0.0035		35	0.19	0.6	78	107	20	6	0.01	1	2	1.5	19	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL24-07	111	113.4	0.051		510	0.66	65	7750	57500	170	16	2	1	55	10.5	134	0.23
KL24-07	113.4	115.3	0.0463		463	0.4	9.9	1000	2520	160	15	2	1	9.1	5.0	46	0.16
KL24-07	115.3	117.5	0.0032		32	0.07	3.1	420	1620	47	7	0.01	1	7.2	2.3	32	0.01
KL24-07	117.5	119.5	0.0024		24	0.1	2.1	131	251	36	8	0.01	1	4.1	0.5	37	0.01
KL24-07	119.5	121.2	0.006		60	0.04	4.2	2360	1040	9	5	1	1	3.7	2.7	27	0.13
KL24-07	121.2	123	0.0022		22	0.03	1.6	197	500	8	9	1	1	1	1.3	20	0.01
KL24-07	123	125.5	0.0013		13	0.02	0.6	40	71	5	4	0.01	1	0.5	1.0	17	0.01
KL24-07	125.5	127.8	0.0012		12	0.01	1.9	170	264	6	11	1	1	0.9	3.7	22	0.01
KL24-07	127.8	129	0.0009		9	0.02	0.1	40	100	4	5	0.01	1	0.4	0.0	21	0.01
KL24-07	129	132	0.0027		27	0.05	3.2	126	640	7	6	5	1	1.2	2.5	24	0.01
KL24-07	132	135	0.0106		106	0.02	4.3	53	1310	27	5	4	1	3.2	4.0	24	0.01
KL24-07	135	138	0.0024		24	0.02	1.5	24	210	6	6	2	4	0.3	4.7	23	0.01
KL24-07	138	141	0.063		630	0.09	20	600	2810	220	10	11	5	16.6	6.2	24	0.01
KL24-07	141	143.8	0.0155		155	0.14	4.8	3700	3010	33	13	6	7	2.1	4.7	28	0.01
KL24-07	143.8	147	0.0035		35	0.04	1.2	310	450	8	4	1	2	0.4	5.5	27	0.01
KL24-07	147	150	0.3		3000	0.57	33	76100	81700	450	30	1	8	24	8.0	28	0.27
KL24-07	150	153	0.0278		278	0.13	5	650	640	93	15	2	11	5.7	3.5	17	0.01
KL24-07	153	160	0.0067		67	0.09	3.8	378	1300	22	18	1	1	3.3	1.2	17	0.01
KL24-07	160	167	0.0103		103	0.03	4.6	670	3380	15	9	0.01	1	4.6	2.0	18	0.01
KL24-07	167	169	0.0037		37	0.04	1.1	225	600	9	10	0.01	1	1.1	3.0	17	0.01
KL24-07	171	173.5	0.0024		24	0.05	0.9	91	410	3	5	0.01	1	0.8	0.9	16	0.01
KL24-07	173.5	175	0.0032		32	0.05	2.3	162	1130	7	7	0.01	1	2	2.0	16	0.01
KL24-07	175	177	0.003		30	0.01	0.8	57	260	5	6	0.01	1	0.6	1.2	17	0.01
KL24-07	177	183	0.0038		38	0.09	3	201	600	29	8	1	1	1.4	3.8	16	0.01
KL24-07	183	185.6	0.0047		47	0.07	8.2	530	2550	66	15	2	1	3.4	2.5	14	0.01
KL24-07	185.6	186	0.0035		35	0.01	1.5	100	350	8	10	0.01	1	0.8	1.7	14	0.01
KL24-07	186	189	0.0036		36	0.17	5.8	333	339	34	11	1	1	2.5	1.3	22	0.1
KL24-07	189	207	0.0068		68	0.11	6.6	430	480	72	51	2	1	2.6	1.7	28	0.01
KL24-07	207	212	0.0115		115	0.08	4.9	207	280	35	11	1	1	2.3	2.0	18	0.01
KL24-07	212	213.7	0.0021		21	0.05	1.2	40	45	6	9	0.01	1	0.8	1.7	16	0.01
KL24-07	213.7	216	0.0027		27	0.06	4.1	830	825	17	8	0.01	1	2.3	1.2	17	0.01
KL24-07	216	219	0.0027		27	0.03	2	330	540	13	3	0.01	1	2	2.3	18	0.01
KL24-07	219	221.8	0.009		90	0.05	3.3	294	400	22	11	0.01	1	2.3	1.5	20	0.01
KL24-07	221.8	223.5	0.0025		25	0.02	2	231	304	13	6	0.01	1	1	4.7	18	0.01
KL24-07	223.5	226.7	0.0427		427	0.15	8.1	1400	2660	91	28	4	1	7	6.1	25	0.34
KL24-07	226.7	228	0.0321		321	0.41	7.1	620	1320	120	221	3	4	6	8.2	76	0.6
KL24-07	228	231	0.0035		35	0.07	1.8	116	157	36	11	0.01	3	1.8	3.0	31	0.01
KL24-07	231	234	0.0111		111	0.08	7.6	2200	2780	23	8	0.01	1	4.3	3.7	21	0.51
KL24-07	234	237	0.0308		308	0.06	18.4	4900	5400	63	13	1	1	13.5	6.5	21	0.32
KL24-07	237	240	0.099		990	0.15	5.1	4100	1760	37	79	11	1	2	7.9	36	0.14
KL24-07	240	243	0.053		530	0.13	31	31700	19400	110	22	2	1	26	14.0	25	0.9
KL24-07	243	246	0.0121		121	0.05	7	8700	4800	7	26	1	1	4.2	4.5	24	0.44
KL24-07	246	249	0.179		1790	0.24	7.8	8400	3400	62	155	19	5	3.4	12.5	45	0.25
KL24-07	249	251	0.0224		224	0.06	7.9	10600	7000	33	17	1	1	7.2	9.5	20	0.36
KL24-07	251	252	0.0081		81	0.03	2	1570	1600	14	8	1	1	1.9	4.8	16	0.1
KL24-07	252	254.5	0.0082		82	0.03	2.1	1040	1220	22	10	2	1	1.7	9.3	26	0.01
KL24-07	254.5	256.5	0.0063		63	0.03	1.3	1070	1060	13	8	0.01	1	1.2	5.8	18	0.11
KL24-07	256.5	258.3	0.078		780	0.17	140	36200	31000	40	17	290	10	4.3	57.0	31	0.96
KL24-07	258.3	261	0.94		9400	1.03	121	139000	48500	2560	270	196	48	126	130.0	170	3.07
KL24-07	261	264	0.23		2300	0.48	117	41300	85500	72	900	258	9	13.5	175.0	100	1.15
KL24-07	264	267	0.49		4900	0.55	98	74600	49700	210	1275	263	21	26	78.0	166	1.71
KL24-07	267	270	0.161		1610	0.33	10	760	1800	130	906	18	5	3.3	10.4	96	0.15
KL24-07	270	273	0.69		6900	0.59	47	45200	5800	190	5250	127	28	2.1	33.2	75	0.91
KL24-07	273	276	0.95		9500	0.79	35.3	4500	1070	210	76	35	24	2	79.0	122	0.01
KL24-07	276	278	0.79		7900	0.83	33.3	2700	960	220	927	35	20	2.8	159.0	148	0.2
KL24-07	278	280	0.401		4010	0.27	20	810	285	70	895	35	23	1.9	67.0	72	0.01
KL24-07	280	282	0.436		4360	0.35	15.8	4300	7400	120	174	24	10	6.1	70.0	43	0.17
KL24-07	282	285	0.233		2330	0.28	12.3	1400	3510	83	239	25	7	3.4	40.0	40	0.21
KL24-07	285	288	0.76		7600	0.57	16.3	1340	1070	74	120	11	11	1.8	53.5	77	0.17
KL24-07	288	291	2.67		26700	1.32	90	8900	5800	310	1475	176	13	4.2	110.0	152	0.41
KL24-07	291	294	0.49		4900	0.61	136	59900	63500	220	1100	288	11	8.3	429.0	141	0.22
KL24-07	294	297	0.89		8900	0.95	77	10900	18300	400	446	125	12	6.1	199.0	160	0.14
KL24-07	297	300	1.62		16200	1.13	70	14000	8700	350	990	106	34	5.8	110.0	143	0.27

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL24-07	300	303	1.35	13500	0.79	72	28300	6400	270	825	154	49	5.2	125.0	104	0.01
KL24-07	303	304	1.61	16100	1.37	36	31900	2700	250	98	63	57	5.5	113.0	105	0.01
KL24-07	304	306.4	0.344	3440	0.33	11.1	3400	2160	110	200	26	13	4.5	38.0	45	0.1
KL24-07	306.4	308.8	0.4	4000	0.3	15	15900	11200	160	50	30	24	8.3	28.3	40	0.01
KL24-07	308.8	311.9	0.0121	121	0.06	2	910	1020	16	20	2	1	1.2	3.3	24	0.18
KL24-07	311.9	315	0.066	660	0.24	5.7	7300	1000	100	179	19	6	2.9	22.0	52	0.01
KL24-07	315	318	0.092	920	0.22	5.5	6500	1240	79	96	21	7	3.7	19.9	34	0.01
KL24-07	318	321	0.061	610	0.11	2.9	4100	460	50	145	11	8	2.3	11.3	34	0.01
KL24-07	321	323	0.195	1950	0.23	3.3	2800	430	57	111	11	9	1.7	11.4	27	0.01
KL24-07	323	325	0.07	700	0.19	2.1	1970	480	50	150	6	5	2.8	6.3	31	0.01
KL24-07	325	327	0.068	680	0.47	7.8	2600	1730	83	49	8	2	5	8.7	35	0.01
KL24-07	327	330	0.119	1190	0.17	8.6	4500	1970	90	45	6	7	5	18.4	36	0.01
KL24-07	330	333	0.086	860	0.16	3.2	1740	610	40	83	5	4	2.1	7.5	28	0.01
KL24-07	333	336	0.14	1400	0.29	16.3	1510	1370	44	29	59	6	1.9	12.2	28	0.01
KL24-07	336	339	0.69	6900	0.35	11.2	2300	1170	110	76	34	16	6	13.7	37	0.01
KL24-07	339	341.7	0.364	3640	0.16	4.2	2100	760	180	52	7	8	12.5	8.0	28	0.01
KL24-07	341.7	345	0.0274	274	0.09	2.3	1030	950	35	20	7	1	2.5	4.5	25	0.01
KL24-07	345	348	0.042	420	0.05	0.8	222	75	14	20	1	1	1	2.0	20	0.01
KL24-07	348	349.6	0.0381	381	0.04	1.2	377	179	14	28	3	1	1.1	3.7	21	0.01
KL24-08	0	3	0.0222	222	0.03	0.1	130	78	17	73	0.01	1	1.1	2.7	24	0.01
KL24-08	3	6	0.0049	49	0.01	0.5	300	157	12	3	0.01	1	1.2	2.5	24	0.01
KL24-08	6	9	0.002	20	0.01	0.1	43	24	6	3	0.01	1	0.4	2.3	23	0.01
KL24-08	9	12	0.0015	15	0.01	0.1	34	18	1	3	0.01	1	0.4	2.5	23	0.01
KL24-08	12	15	0.0027	27	0.01	0.1	42	18	4	1	0.01	1	0.4	1.8	25	0.01
KL24-08	15	18	0.0018	18	0.04	0.1	74	28	17	3	0.01	1	1.2	2.8	24	0.01
KL24-08	18	21	0.001	10	0.02	0.1	38	43	10	1	0.01	1	0.9	3.0	25	0.01
KL24-08	21	24	0.0021	21	0.01	0.1	43	27	4	2	0.01	1	0.6	2.5	36	0.01
KL24-08	24	27	0.0013	13	0.01	0.1	54	67	12	1	0.01	1	0.8	1.5	32	0.01
KL24-08	27	29.5	0.0017	17	0.02	0.1	45	51	14	1	0.01	1	1	2.0	33	0.01
KL24-08	29.5	32.6	0.0009	9	0.04	0.1	77	24	36	1	0.01	1	0.8	2.3	31	0.01
KL24-08	32.6	35.7	0.0011	11	0.02	0.1	80	46	33	1	0.01	1	0.9	2.3	26	0.01
KL24-08	35.7	39	0.0011	11	0.03	0.1	75	70	19	1	0.01	1	1.2	2.2	34	0.01
KL24-08	39	42	0.0008	8	0.01	0.1	27	29	9	1	0.01	1	0.8	2.5	36	0.01
KL24-08	42	45	0.0011	11	0.01	0.1	440	126	17	1	0.01	1	2.1	3.0	34	0.01
KL24-08	45	48.25	0.001	10	0.01	0.1	36	18	17	1	0.01	1	0.6	1.5	28	0.01
KL24-08	48.25	51	0.0014	14	0.01	0.1	21	24	9	1	0.01	1	0.7	1.8	25	0.01
KL24-08	51	54	0.0011	11	0.01	0.1	27	21	4	1	0.01	1	0.6	2.3	25	0.01
KL24-08	54	56.9	0.0025	25	0.01	0.6	40	184	7	1	0.01	1	0.8	4.0	27	0.01
KL24-08	56.9	60	0.0041	41	0.01	0.8	57	184	8	1	0.01	1	1.3	4.2	48	0.01
KL24-08	60	62.9	0.0036	36	0.01	0.7	54	61	11	1	0.01	1	1	3.2	43	0.01
KL24-08	62.9	66	0.0015	15	0.04	1.4	181	372	24	1	0.01	1	1.7	3.0	124	0.01
KL24-08	66	68.5	0.021	210	0.01	1.6	360	500	20	9	0.01	1	1.2	2.8	130	0.01
KL24-08	68.5	71.75	0.395	3950	0.14	1.3	367	26	5	2	2	17	0.01	1.9	20	0.01
KL24-08	71.75	74.1	0.0023	23	0.05	2.4	107	186	42	11	2	6	2	10.8	96	0.01
KL24-08	74.1	77.2	0.0046	46	0.09	5.5	510	570	28	69	5	1	2.3	10.8	63	0.01
KL24-08	77.2	80.45	0.0029	29	0.18	9.1	1210	1830	21	9	2	1	8.3	6.7	31	0.01
KL24-08	80.45	83	0.0193	193	5.21	25.4	9000	7700	340	105	6	7	28	50.0	208	0.26
KL24-08	83	86.7	0.0175	175	3.27	13.9	2900	1890	270	35	2	4	19.4	29.4	209	0.21
KL24-08	86.7	89.7	0.0024	24	0.16	2.3	101	178	25	6	4	1	1.3	4.8	314	0.01
KL24-08	89.7	91.1	0.0028	28	0.26	1.4	171	151	31	6	1	1	1.6	4.0	268	0.01
KL24-08	91.1	93	0.0154	154	0.49	12	3100	3400	270	8	16	1	9.8	13.5	52	0.11
KL24-08	93	95	0.0096	96	0.3	4	420	730	140	5	2	1	8.7	3.0	60	0.01
KL24-08	95	98	0.0074	74	0.35	12	1130	8800	220	14	10	1	15.8	7.4	262	0.01
KL24-08	98	101	0.0023	23	0.05	1	149	175	19	22	0.01	1	2.6	0.7	92	0.01
KL24-08	101	104	0.0014	14	0.11	1.3	66	117	16	8	0.01	1	2	0.5	226	0.01
KL24-08	104	106.5	0.0015	15	0.04	1	45	60	9	5	1	1	0.9	1.8	249	0.01
KL24-08	106.5	109.3	0.0015	15	0.04	1	70	61	14	4	0.01	1	1.8	1.5	181	0.01
KL24-08	109.3	111	0.002	20	0.07	1.4	90	156	38	5	0.01	1	2.6	1.8	293	0.01
KL24-08	111	113.6	0.0013	13	0.08	0.1	47	57	20	7	0.01	1	1.2	0.0	227	0.01
KL24-08	113.6	121.5	0.002	20	0.02	1.5	258	1590	17	6	0.01	1	4.4	1.0	214	0.01
KL24-08	121.5	124.8	0.0022	22	0.03	1.8	281	1900	15	4	0.01	1	5.4	2.2	130	0.01
KL24-08	124.8	126	0.002	20	0.01	0.7	120	286	5	6	0.01	1	2.6	0.0	93	0.01
KL24-08	126	129	0.0026	26	0.05	0.8	261	600	19	4	0.01	1	3.1	0.0	50	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL24-08	129	132	0.0032		32	0.01	0.1	45	144	5	6	0.01	1	1.7	0.0	13	0.01
KL24-08	132	134.5	0.0043		43	0.01	0.1	67	230	7	12	0.01	1	3.1	0.0	11	0.01
KL24-08	134.5	136.7	0.0036		36	0.01	0.1	77	135	8	4	0.01	1	3.7	0.0	79	0.01
KL24-08	136.7	138.55	0.0049		49	0.02	0.1	80	160	7	6	0.01	1	2.6	2.0	80	0.01
KL24-08	138.55	141	0.0031		31	0.01	0.1	57	267	10	8	0.01	1	2.5	0.0	36	0.01
KL24-08	141	144	0.0035		35	0.01	1.8	127	710	10	12	0.01	1	4.2	1.3	47	0.01
KL24-08	144	147	0.0013		13	0.01	0.8	52	84	9	13	0.01	1	1.4	0.5	80	0.01
KL24-08	147	150	0.0017		17	0.01	0.1	30	58	8	8	0.01	1	2	0.0	96	0.01
KL24-08	150	153	0.0011		11	0.01	0.1	26	30	6	5	0.01	1	0.3	0.5	50	0.01
KL24-08	153	156	0.0013		13	0.01	0.1	18	14	5	4	0.01	1	0.3	0.8	64	0.01
KL24-08	156	159.2	0.0014		14	0.03	0.1	31	18	3	2	0.01	1	0.2	0.0	34	0.01
KL24-08	159.2	165	0.0017		17	0.33	0.7	39	62	13	5	0.01	1	0.7	2.0	38	0.01
KL24-08	165	171	0.0023		23	0.07	0.6	50	287	7	3	0.01	1	1.2	0.8	36	0.01
KL24-08	171	174	0.0021		21	0.08	1.2	207	820	16	6	0.01	1	1.8	1.8	15	0.01
KL24-08	174	178.3	0.0025		25	0.29	3.5	840	1810	33	10	0.01	1	4.1	5.0	18	0.01
KL24-08	178.3	183	0.005		50	0.13	3.4	1480	2350	22	10	1	1	3.5	4.3	13	0.01
KL24-08	183	186	0.01		100	0.24	11.6	214	6400	70	15	2	6	10.7	9.2	26	0.01
KL24-08	186	201	0.0028		28	0.12	3	410	1190	16	6	3	1	0.8	5.5	20	0.01
KL24-08	201	205	0.0048		48	0.07	3.2	480	2100	36	46	0.01	1	3.2	4.0	22	0.01
KL24-08	205	210	0.0067		67	0.05	1.7	137	1280	92	90	1	1	3.1	3.8	34	0.01
KL24-08	210	218	0.154		1540	0.61	64	28600	33400	820	9	4	11	56	47.5	50	0.55
KL24-08	218	222	0.0071		71	0.09	3.3	194	281	90	4	0.01	13	1.4	4.0	30	0.01
KL24-08	222	225.4	0.17		1700	0.34	170	18800	214000	380	9	12	7	24.2	26.3	32	0.42
KL24-08	225.4	228.3	0.0033		33	0.36	5.6	370	1170	68	10	4	14	4.3	7.8	40	0.1
KL24-08	228.3	232.1	0.0064		64	0.22	3.9	580	1370	62	7	2	16	6.3	16.0	48	0.01
KL24-08	232.1	236	0.0049		49	0.2	7.3	204	9000	66	13	4	12	9.2	12.3	40	0.01
KL24-08	236	239	0.0102		102	0.55	67	830	27100	200	150	129	29	9.6	102.0	52	0.16
KL24-08	239	242	0.064		640	0.79	85	3600	58600	270	238	108	28	13.8	396.0	61	0.11
KL24-08	242	243	0.118		1180	0.68	166	24600	274000	630	17	135	17	62	226.0	97	0.43
KL24-08	243	246	0.09		900	0.22	42	39400	60700	86	16	10	7	28	57.8	23	0.3
KL24-08	246	249	0.0352		352	0.08	19.5	2600	14900	81	23	12	1	18	7.0	24	0.12
KL24-08	249	251	0.01		100	0.15	21	1390	6600	47	113	32	3	2.7	9.5	30	0.12
KL24-08	251	254	0.0085		85	0.1	13.1	3500	7500	29	68	12	1	6	6.5	27	0.21
KL24-08	254	257.1	0.0425		425	0.21	30.5	18000	30400	92	89	12	3	19.3	15.3	43	0.54
KL24-08	257.1	260.2	0.0045		45	0.1	5.5	1490	2630	30	30	5	1	1.7	5.0	23	0.28
KL24-08	260.2	263.3	0.007		70	0.06	4	1520	1990	23	11	2	1	1.1	8.4	27	0.25
KL24-08	263.3	266	0.0046		46	0.09	3.9	1030	1800	25	15	2	1	0.9	7.5	18	0.38
KL24-08	266	269	0.0091		91	0.12	3.6	1630	2430	23	47	2	1	1.8	8.3	16	0.27
KL24-08	269	272.2	0.0099		99	0.14	3.7	1100	3250	33	15	1	1	1.5	11.3	42	0.41
KL24-08	272.2	275.3	0.0049		49	0.09	3.6	1400	1450	16	12	2	1	1.2	9.0	26	0.4
KL24-08	275.3	278.3	0.0203		203	0.08	9.8	1800	5700	39	41	9	1	2.3	23.0	33	0.23
KL24-08	278.3	281.3	0.022		220	0.1	11.2	3900	5500	60	146	4	1	5.6	30.5	37	0.39
KL24-08	281.3	284.3	0.0357		357	0.08	18.7	10300	14900	49	33	3	1	7.8	56.3	24	0.42
KL24-08	284.3	287.4	0.008		80	0.04	4.2	2400	3000	17	11	1	1	1.1	38.5	18	0.12
KL24-08	287.4	290.5	0.0207		207	0.1	12.4	11400	12500	58	61	2	1	5.3	42.3	37	0.3
KL24-08	290.5	293.6	0.138		1380	0.12	31	17000	19900	180	25	5	1	10	50.0	48	0.46
KL24-08	293.6	296.7	0.0435		435	0.1	27.3	18300	22500	61	11	4	1	9.5	42.5	32	0.41
KL24-08	296.7	299.8	0.0104		104	0.05	7.2	3800	4600	28	18	2	1	1.6	18.0	31	0.14
KL24-08	299.8	302.9	0.0098		98	0.05	8.9	4100	5000	22	30	3	1	3.5	20.3	28	0.12
KL24-08	302.9	306	0.0169		169	0.05	12.9	8600	6500	34	46	5	1	4.6	19.8	24	0.16
KL24-08	306	308.5	0.124		1240	0.11	33	40400	31900	60	72	4	1	18.5	85.0	32	0.1
KL24-08	308.5	311.5	0.28		2800	0.19	34	21300	22900	260	78	25	3	9.1	72.5	82	0.01
KL24-08	311.5	314	0.31		3100	0.12	28.4	13900	19900	170	74	2	4	6.2	95.0	36	0.01
KL24-08	314	317.5	0.082		820	0.18	33.2	41600	19700	72	41	76	18	4	180.0	35	0.01
KL24-08	317.5	320.75	0.0121		121	0.07	4.6	2300	2600	35	67	6	1	1.3	40.0	23	0.01
KL24-08	320.75	323.6	0.149		1490	0.13	8.2	20600	2500	210	208	160	16	6.2	67.5	76	0.01
KL24-08	323.6	326.6	0.36		3600	0.19	5.4	9300	910	220	1057	68	10	7.8	45.0	92	0.01
KL24-08	326.6	329.6	0.176		1760	0.23	12.3	18100	890	210	1020	96	11	5.3	49.0	116	0.01
KL24-08	329.6	332.7	0.41		4100	0.43	41	112000	14300	220	228	160	82	7	205.0	246	0.01
KL24-08	332.7	335.7	0.31		3100	0.57	91	50900	21500	210	393	210	33	5.2	260.0	215	0.01
KL24-08	335.7	338.7	0.3		3000	0.49	54	47500	23700	290	188	120	24	19.7	220.0	194	0.01
KL24-08	338.7	341.8	0.075		750	0.2	10.1	10700	4300	85	48	14	7	3.6	36.5	72	0.01
KL24-08	341.8	344.8	0.063		630	0.15	6.7	4200	2200	67	28	5	4	5.8	11.0	32	0.11

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL24-08	344.8	347.9	0.054		540	0.13	7.4	3000	2500	63	40	7	4	3.9	17.3	38	0.11
KL24-08	347.9	349.4	0.086		860	0.14	6.6	2300	1810	45	26	8	4	2.3	16.5	34	0.01
KL24-08	349.4	350.9	0.101		1010	0.08	3.3	870	550	30	15	2	4	1.5	7.5	22	0.01
KL24-08	350.9	353.9	0.057		570	0.05	4	1450	720	12	28	13	2	0.7	11.3	20	0.01
KL24-08	353.9	357	0.066		660	0.13	9.4	5800	9600	63	27	8	3	7.1	18.3	26	0.01
KL24-08	357	360	0.0323		323	0.11	21.3	16000	28100	24	26	8	1	24	210.0	21	0.01
KL24-08	360	363	0.0089		89	0.02	4.1	990	1630	9	7	2	1	3.6	10.3	20	0.01
KL24-08	363	366	0.0086		86	0.04	42	14300	15000	6	7	2	1	51	7.0	20	0.01
KL24-08	366	369	0.008		80	0.03	30.2	10400	10300	13	13	1	1	30	3.5	17	0.01
KL24-08	369	372	0.0083		83	0.03	13.2	3300	3700	7	23	2	1	10.7	4.5	20	0.01
KL24-08	372	375	0.0198		198	0.05	11.2	2700	2700	34	23	5	1	6.7	4.8	21	0.01
KL24-08	375	378	0.0212		212	0.05	4.9	1900	1530	40	17	4	2	3	4.8	21	0.01
KL24-08	378	381	0.0236		236	0.07	11.8	10000	15000	17	17	7	1	13.2	100.0	19	0.01
KL24-08	381	384	0.0138		138	0.09	2.8	910	700	34	19	3	1	2.8	2.5	20	0.01
KL24-08	384	388	0.0132		132	0.1	2.4	630	580	24	24	2	1	2.2	2.0	21	0.01
KL24-09	0	3	0.0031		31	0.01	0.1	70	50	8	2	0.01	1	0.4	0.8	22	0.01
KL24-09	3	6	0.0035		35	0.01	0.1	87	40	9	3	0.01	1	1.1	1.1	19	0.01
KL24-09	6	9	0.0043		43	0.01	0.1	31	28	4	9	0.01	1	1.5	0.0	24	0.01
KL24-09	9	12	0.0035		35	0.01	0.1	31	20	5	3	0.01	1	0.4	1.1	17	0.01
KL24-09	12	15	0.003		30	0.01	0.1	40	20	4	2	0.01	1	0.4	0.9	20	0.01
KL24-09	15	18	0.0051		51	0.04	7.7	140	58	11	2	0.01	1	2.4	2.8	30	0.01
KL24-09	18	21	0.0037		37	0.06	0.6	168	65	18	3	0.01	1	1.4	2.1	34	0.01
KL24-09	21	24	0.0029		29	0.03	0.1	450	121	11	3	0.01	1	0.9	1.9	27	0.01
KL24-09	24	27	0.0045		45	0.01	0.1	500	89	6	1	0.01	1	0.5	1.0	19	0.01
KL24-09	27	30	0.0038		38	0.02	0.1	113	37	11	3	0.01	1	1.1	0.8	20	0.01
KL24-09	30	33	0.0045		45	0.03	0.1	77	37	12	4	0.01	1	1	1.2	25	0.01
KL24-09	33	36.6	0.0061		61	0.11	14.3	248	89	23	3	0.01	1	4.5	5.5	35	0.01
KL24-09	36.6	38.7	0.004		40	0.09	1.3	180	80	16	4	0.01	1	1.4	2.8	40	0.01
KL24-09	38.7	41.8	0.0034		34	0.03	0.1	91	43	12	5	0.01	1	1.7	1.3	35	0.01
KL24-09	41.8	44.8	0.0042		42	0.01	0.1	115	45	11	5	0.01	1	1.4	1.4	32	0.01
KL24-09	44.8	47.8	0.0039		39	0.03	0.7	760	374	15	6	0.01	3	1.9	1.2	27	0.01
KL24-09	47.8	50.8	0.0048		48	0.01	0.1	286	172	7	4	0.01	2	0.7	1.1	34	0.01
KL24-09	50.8	54	0.0025		25	0.01	0.1	198	137	17	5	0.01	3	0.9	1.4	46	0.01
KL24-09	54	57	0.003		30	0.01	0.1	23	21	12	3	0.01	1	0.6	1.5	32	0.01
KL24-09	57	60	0.0056		56	0.01	0.1	36	40	11	3	0.01	1	0.9	1.1	39	0.01
KL24-09	60	65.4	0.002		20	0.01	0.1	33	32	11	2	0.01	1	0.8	1.2	26	0.01
KL24-09	65.4	69	0.0034		34	0.01	0.1	23	21	15	2	0.01	1	0.5	1.1	30	0.01
KL24-09	69	72	0.002		20	0.01	0.1	33	17	7	2	0.01	1	0.3	0.9	30	0.01
KL24-09	72	75	0.0034		34	0.01	0.1	25	14	4	2	0.01	1	0.2	1.4	21	0.01
KL24-09	75	78	0.004		40	0.01	0.1	26	20	5	2	0.01	1	0.7	1.1	25	0.01
KL24-09	78	81	0.0028		28	0.01	0.1	35	17	4	2	0.01	1	0.2	1.0	26	0.01
KL24-09	81	83.1	0.006		60	0.01	0.1	74	46	3	4	0.01	1	0.5	0.9	46	0.01
KL24-09	83.1	86	0.0024		24	0.01	0.1	29	17	4	2	0.01	1	0.01	1.9	25	0.01
KL24-09	86	88.5	0.0043		43	0.01	0.1	28	20	3	2	0.01	1	0.01	2.7	21	0.01
KL24-09	88.5	91	0.0052		52	0.01	0.1	30	20	4	3	0.01	1	0.01	1.8	23	0.01
KL24-09	91	93	0.0018		18	0.01	0.1	31	14	3	1	0.01	1	0.01	1.9	18	0.01
KL24-09	93	94.5	0.0018		18	0.01	0.1	38	12	2	1	0.01	1	0.2	2.0	17	0.01
KL24-09	94.5	97.5	0.005		50	0.01	0.1	36	16	1	2	0.01	1	0.01	2.7	23	0.01
KL24-09	97.5	99	0.004		40	0.01	0.1	23	13	3	2	0.01	1	0.01	0.7	18	0.01
KL24-09	99	102	0.0064		64	0.01	0.1	33	17	6	3	0.01	1	0.6	0.8	19	0.01
KL24-09	102	105	0.0062		62	0.03	0.1	30	19	8	1	0.01	1	0.5	0.9	25	0.01
KL24-09	105	106.65	0.0045		45	0.03	2.6	337	620	10	3	0.01	1	2.3	3.1	21	0.01
KL24-09	106.65	108	0.0057		57	0.04	2.2	257	530	11	4	2	1	1.6	3.8	25	0.01
KL24-09	108	111	0.0036		36	0.01	0.1	77	90	7	1	0.01	1	1	3.4	26	0.01
KL24-09	111	113.5	0.0052		52	0.01	0.7	67	285	8	2	0.01	1	1.6	5.1	45	0.01
KL24-09	113.5	116.6	0.0083		83	0.01	0.1	48	215	6	2	0.01	1	1.2	2.9	38	0.01
KL24-09	116.6	117.65	0.005		50	0.01	0.1	55	139	5	2	0.01	1	1.4	5.1	25	0.01
KL24-09	117.65	119.3	0.0027		27	0.01	1.1	111	59	24	2	0.01	7	0.9	1.3	75	0.01
KL24-09	119.3	123	0.0027		27	0.01	0.1	65	125	10	1	0.01	1	0.6	1.2	44	0.01
KL24-09	123	126.4	0.004		40	0.01	0.1	55	104	15	1	0.01	2	1.4	0.8	56	0.01
KL24-09	126.4	128.4	0.0044		44	1.07	16.7	3550	1900	100	16	17	1	8	13.6	381	0.01
KL24-09	128.4	132	0.001		10	0.04	0.1	65	54	39	1	0.01	7	1.4	1.0	92	0.01
KL24-09	132	134.4	0.0018		18	0.25	1.2	70	171	48	4	0.01	6	2.3	2.8	81	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL24-09	134.4	138	0.007		70	0.17	5.9	540	1200	19	7	7	1	1.8	4.0	14	0.01
KL24-09	138	141	0.0101		101	0.17	6.5	550	1170	25	5	7	1	1.9	4.0	18	0.01
KL24-09	141	144	0.0026		26	0.19	4.3	410	930	17	41	2	1	1.1	2.9	15	0.01
KL24-09	144	147	0.0048		48	0.05	5.1	810	1530	9	8	1	1	2.3	2.6	15	0.01
KL24-09	147	149.6	0.0141		141	0.1	3.6	930	1150	16	21	4	1	1.9	2.9	17	0.01
KL24-09	149.6	152.7	0.0048		48	0.38	10.3	2550	3700	31	6	6	1	8.9	4.0	144	0.1
KL24-09	152.7	155	0.0042		42	0.32	8.6	1870	2050	27	8	3	1	6.6	5.3	298	0.01
KL24-09	155	157.3	0.0014		14	0.02	0.1	63	48	18	3	0.01	4	1.3	1.5	140	0.01
KL24-09	157.3	160.5	0.0018		18	0.33	0.9	145	104	22	1	0.01	1	3.2	0.8	30	0.01
KL24-09	160.5	164	0.001		10	0.41	1.3	68	102	21	4	0.01	1	3.5	1.0	48	0.01
KL24-09	164	166	0.0017		17	0.68	2.4	61	127	28	14	0.01	1	2.4	0.8	113	0.01
KL24-09	166	169	0.0019		19	0.35	3.4	69	150	47	18	0.01	1	2.1	1.9	70	0.01
KL24-09	169	172	0.0021		21	0.94	4.8	145	104	36	15	0.01	1	7	1.5	308	0.1
KL24-09	172	175.5	0.0021		21	0.35	5.1	84	108	42	22	0.01	1	2.9	1.2	206	0.01
KL24-09	175.5	178.3	0.005		50	0.09	1.4	38	42	11	6	0.01	1	2	0.8	24	0.01
KL24-09	178.3	181.2	0.0023		23	0.09	3	183	187	14	7	0.01	1	1.9	0.7	200	0.01
KL24-09	181.2	184.4	0.0017		17	0.1	3.1	106	264	22	6	0.01	1	1.7	1.6	307	0.01
KL24-09	184.4	188	0.0027		27	0.07	1.1	45	79	20	7	0.01	1	1.6	1.1	199	0.01
KL24-09	188	191	0.0034		34	0.05	1.2	64	100	26	7	0.01	1	1.1	0.7	320	0.01
KL24-09	191	195	0.0031		31	0.04	0.8	55	32	10	5	0.01	1	0.3	0.0	238	0.01
KL24-09	195	201	0.0026		26	0.06	2.9	113	121	16	5	0.01	1	2.3	1.0	232	0.01
KL24-09	201	204	0.004		40	0.08	5.7	740	1540	14	7	5	1	3.7	2.1	127	0.01
KL24-09	204	207	0.002		20	0.04	2.8	188	750	35	6	0.01	1	2.8	3.2	165	0.01
KL24-09	207	209.2	0.0024		24	0.02	2.3	240	450	28	5	0.01	1	3	1.8	320	0.01
KL24-09	209.2	211.7	0.0044		44	0.02	0.9	108	107	8	5	0.01	1	0.2	0.8	255	0.01
KL24-09	211.7	214	0.0161		161	0.03	2.9	650	351	29	10	0.01	1	2	2.3	38	0.01
KL24-09	214	216	0.0073		73	0.01	0.1	2500	42	7	4	0.01	3	0.6	0.6	191	0.01
KL24-09	216	219	0.0033		33	0.02	0.1	78	21	2	6	0.01	1	0.2	0.0	229	0.01
KL24-09	219	222	0.0076		76	0.01	0.1	41	29	0.01	4	0.01	1	0.01	0.6	163	0.01
KL24-09	222	225	0.0084		84	0.04	29	1470	1890	28	7	65	1	4.3	9.3	185	0.1
KL24-09	225	228	0.0013		13	0.06	1	23	34	4	4	0.01	1	0.2	0.0	185	0.01
KL24-09	228	231	0.0016		16	0.04	1.4	11	10	3	5	0.01	1	0.6	0.5	173	0.01
KL24-09	231	234	0.0015		15	0.1	2.4	18	11	4	7	0.01	1	0.2	0.5	168	0.01
KL24-09	234	237	0.0015		15	0.13	7.8	57	145	29	4	0.01	1	7.5	0.7	197	0.01
KL24-09	237	240	0.0012		12	0.11	3.6	120	73	19	6	0.01	1	5.4	0.0	109	0.1
KL24-09	240	243	0.0175		175	0.06	1.7	26	20	8	13	0.01	1	0.6	0.7	99	0.01
KL24-09	243	246	0.002		20	0.09	2.2	29	27	14	16	0.01	1	0.9	0.9	222	0.01
KL24-09	246	249	0.0017		17	0.11	1.3	35	24	12	8	0.01	1	1	0.6	161	0.01
KL24-09	249	251.5	0.0056		56	0.09	1	294	100	22	18	0.01	1	2.3	1.4	144	0.01
KL24-09	251.5	254.6	0.0154		154	0.11	4.3	285	720	32	9	0.01	1	6.8	6.7	28	0.01
KL24-09	254.6	258	0.002		20	0.08	2.4	130	170	21	10	1	1	3.1	2.7	212	0.01
KL24-09	258	260.1	0.0034		34	0.18	2	95	178	29	6	1	1	3.8	2.9	104	0.01
KL24-09	260.1	262.5	0.0057		57	0.41	6.1	124	440	36	10	2	1	7.7	5.7	26	0.01
KL24-09	262.5	264	0.0044		44	0.5	4.3	125	193	37	6	2	1	7.6	3.1	30	0.1
KL24-09	264	267	0.0045		45	0.25	6.5	363	980	69	13	7	1	4.5	6.6	37	0.01
KL24-09	267	273	0.0101		101	0.25	6.1	172	600	41	34	6	1	3.7	3.7	78	0.1
KL24-09	273	276	0.201		2010	0.86	61	20900	8060	360	128	58	15	36	15.3	40	0.18
KL24-09	276	280.2	0.0052		52	0.16	1.9	149	81	18	15	2	1	2.9	3.5	24	0.01
KL24-09	280.2	283.5	0.0032		32	0.21	1.8	30	82	22	14	2	1	1.7	5.4	22	0.01
KL24-09	283.5	287.9	0.0018		18	0.16	1	32	73	11	37	2	1	0.8	1.4	20	0.01
KL24-09	287.9	291	0.004		40	0.12	1.4	64	74	10	29	1	1	0.9	0.7	21	0.01
KL24-09	291	294	0.0055		55	0.11	4	323	670	26	33	3	1	3.6	4.8	16	0.01
KL24-09	294	297	0.0051		51	0.07	6.3	430	760	24	52	8	1	1.9	6.3	13	0.01
KL24-09	297	300	0.0038		38	0.05	3.1	140	249	14	100	2	1	1.3	2.3	14	0.01
KL24-09	300	303	0.0029		29	0.1	4.2	1000	1140	18	86	1	1	3.4	5.2	18	0.1
KL24-09	303	306	0.0067		67	0.09	5	2800	3000	17	74	1	1	4.3	10.3	20	0.13
KL24-09	306	309	0.0022		22	0.06	3.7	352	780	15	70	1	1	2.4	4.0	21	0.1
KL24-09	309	312	0.0035		35	0.13	4	790	780	15	42	1	1	1.8	3.6	20	0.1
KL24-09	312	315	0.0023		23	0.02	2.4	1030	1340	13	8	0.01	1	2.8	4.6	20	0.01
KL24-09	315	318	0.0012		12	0.01	1.2	345	890	12	5	0.01	1	1.8	2.9	18	0.01
KL24-09	318	321	0.0034		34	0.01	5.4	630	4450	17	4	3	1	4.7	7.1	20	0.01
KL24-09	321	324	0.0036		36	0.04	1.6	347	890	13	6	1	1	1.1	3.2	18	0.01
KL24-09	324	326.5	0.002		20	0.03	1	70	430	11	7	1	1	0.6	2.3	18	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL24-09	326.5	330	0.0049		49	0.02	1.6	110	1730	13	7	1	1	1.5	4.0	18	0.01
KL24-09	330	346	0.0018		18	0.03	1	46	990	12	27	0.01	1	1.6	3.8	17	0.01
KL24-09	346	348	0.0026		26	0.06	1.5	820	1470	93	110	1	6	3.8	6.3	31	0.01
KL24-09	348	351	0.0009		9	0.07	0.1	34	51	120	14	0.01	3	3.7	1.1	14	0.01
KL24-09	351	354	0.0013		13	0.58	0.1	28	14	150	14	0.01	6	4.6	3.1	24	0.38
KL24-09	354	357	0.0021		21	0.08	0.1	35	19	110	14	0.01	4	3.5	0.7	27	0.1
KL24-09	357	360	0.44		4400	0.8	1.4	104	53	28	6	1	10	1.1	3.2	24	0.01
KL24-09	360	363	0.026		260	0.12	8.1	229	2520	100	122	10	18	6.1	26.0	24	0.01
KL24-09	363	366	0.019		190	0.19	12.8	3400	7810	42	25	14	3	6.7	28.8	24	0.1
KL24-09	366	369.5	0.0096		96	0.04	8.6	530	1700	30	13	30	1	7.3	14.9	25	0.01
KL24-09	369.5	371.5	0.012		120	0.06	10.8	1450	4900	33	20	21	7	5.8	27.0	27	0.01
KL24-09	371.5	375	0.0086		86	0.04	6	1150	3100	19	8	7	1	9.5	11.3	21	0.01
KL24-09	375	378	0.0201		201	0.2	12.6	2100	2740	44	45	21	2	4.2	16.1	27	0.01
KL24-09	378	382.7	0.424		4240	0.36	198	22800	7000	1380	14	37	6	102	15.0	28	0.26
KL24-09	382.7	384	0.263		2630	0.25	99	31500	30400	430	21	36	8	42	71.5	41	0.31
KL24-09	384	387	0.0324		324	0.07	9.7	3250	3600	44	21	4	1	4.3	11.3	20	0.15
KL24-09	387	389.5	0.136		1360	0.23	134	9100	61600	300	27	48	3	162	141.0	20	0.01
KL24-09	389.5	392.6	0.0187		187	0.18	9.4	1470	2830	55	12	2	1	6.3	7.8	14	0.01
KL24-09	392.6	395.7	0.0108		108	0.13	7.4	1550	2550	24	21	1	1	5.6	9.7	16	0.01
KL24-09	395.7	398.7	0.0275		275	0.09	5.4	1630	2870	22	29	2	1	4.7	8.9	21	0.01
KL24-09	398.7	401.9	0.0148		148	0.14	13.7	4700	9800	23	24	8	1	9.9	25.0	16	0.01
KL24-09	401.9	404.9	0.0105		105	0.09	14.8	3300	4900	26	28	25	1	3.5	12.2	18	0.01
KL24-09	404.9	408	0.0314		314	0.08	6.7	1810	870	24	33	16	3	7	12.3	23	0.01
KL24-09	408	411	0.012		120	0.09	2.9	950	580	40	63	6	4	2.7	10.3	19	0.01
KL24-09	411	414	0.0367		367	0.09	6.8	3180	750	120	25	10	6	5.2	15.1	22	0.01
KL24-09	414	415.8	0.053		530	0.12	8	6300	1100	80	70	9	7	5.5	16.0	84	0.01
KL24-09	415.8	417	0.18		1800	0.95	85	49300	49300	320	107	52	18	40	341.0	241	0.01
KL24-09	417	420.5	0.072		720	0.76	54	26200	33200	350	68	37	12	40	334.0	226	0.16
KL24-09	420.5	423	0.058		580	0.47	33	12400	16900	160	3500	76	8	16	141.0	87	0.01
KL24-09	423	426	0.0297		297	0.12	6.3	580	980	120	3400	41	21	3.2	27.0	24	0.01
KL24-09	426	429	0.0265		265	0.26	12.5	820	2320	120	2400	52	13	3.8	36.0	24	0.01
KL24-09	429	432	0.0172		172	0.48	5.4	980	1570	110	1360	18	15	3.1	27.0	15	0.01
KL24-09	432	435	0.114		1140	0.76	15	4000	4050	160	470	26	7	6	49.0	48	0.16
KL24-09	435	438	0.099		990	0.94	27.5	7300	10300	160	300	54	13	16.5	77.0	64	0.13
KL24-09	438	441	0.14		1400	1.75	39	9000	15000	180	280	96	20	20	87.0	100	0.12
KL24-09	441	443	0.991		9910	5.43	173	38200	24300	210	216	1530	110	20	359.0	131	0.01
KL24-09	443	446.3	0.281		2810	0.34	26.8	7900	2590	130	760	208	41	4.2	91.0	87	0.01
KL24-09	446.3	449.7	0.0182		182	0.1	11.7	6400	5700	52	37	23	4	7.2	88.0	41	0.01
KL24-09	449.7	453	0.032		320	0.09	8.5	560	1510	32	163	25	6	3.1	20.0	37	0.01
KL24-09	453	456	0.0039		39	0.05	1.5	165	450	31	106	3	5	1.8	4.8	20	0.01
KL24-09	456	459	0.0026		26	0.05	18.6	410	9210	34	250	34	2	3.8	41.0	21	0.01
KL24-09	459	462	0.0082		82	0.04	15	980	3300	26	310	34	3	3.4	32.0	21	0.01
KL24-09	462	463.5	0.108		1080	0.33	48	8100	8930	58	196	169	49	4.2	237.0	34	0.01
KL24-09	463.5	466.7	0.007		70	0.12	6.8	2200	1920	66	11	3	4	10.2	7.0	40	0.01
KL24-09	466.7	469.5	0.0055		55	0.13	9.9	7800	3780	80	10	1	3	13.3	5.9	43	0.33
KL24-09	469.5	471.4	0.0076		76	0.12	7.7	6000	2790	97	7	0.01	2	16.1	5.9	40	0.25
KL24-09	471.4	473	0.121		1210	0.2	11.1	1020	1570	49	420	45	17	6.4	46.0	40	0.01
KL24-09	473	477	0.0105		105	0.16	6.2	2850	1570	110	7	2	3	11.7	7.9	40	0.13
KL24-09	477	480	0.0116		116	0.17	6.3	1600	1230	120	20	5	3	9	14.7	38	0.01
KL24-09	480	483	0.0151		151	0.16	16.6	1980	1170	100	27	4	5	6.3	15.4	41	0.01
KL24-09	483	484.7	0.0102		102	0.11	4.8	420	330	48	12	32	4	4.2	6.5	34	0.01
KL24-09	484.7	486	0.062		620	0.07	6.3	510	810	64	206	170	82	7	54.0	30	0.01
KL24-09	486	488.6	0.0078		78	0.08	3.1	242	205	36	147	20	6	4.5	7.4	27	0.01
KL24-09	488.6	490.3	0.0323		323	0.13	3.3	920	580	54	290	104	33	4.9	32.0	24	0.01
KL24-09	490.3	493.9	0.0298		298	0.15	1.6	600	352	81	29	7	14	5.4	4.5	37	0.01
KL24-09	493.9	496	0.0202		202	0.13	5.4	780	740	56	128	56	9	5.1	54.0	34	0.01
KL24-09	496	498.6	0.0226		226	0.15	6.7	930	830	100	32	42	9	7.9	45.0	47	0.01
KL24-09	498.6	501	0.0194		194	0.15	3.5	870	560	130	62	30	9	7.1	20.0	43	0.01
KL24-09	501	503.5	0.0106		106	0.06	1.1	258	186	58	97	11	8	3.1	5.3	20	0.01
KL24-09	503.5	507	0.0233		233	0.11	2.1	1200	303	54	10	15	15	1.8	4.8	31	0.01
KL24-09	507	509	0.0109		109	0.19	2.7	1080	630	76	4	8	9	2.5	12.3	21	0.01
KL24-09	509	511.25	0.0215		215	0.16	2.8	360	207	31	7	2	12	3.1	4.8	45	0.01
KL24-09	511.25	513	0.0059		59	0.13	5.1	1510	1520	50	6	6	3	7.9	10.8	20	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL24-09	513	519	0.0022		22	0.06	0.1	83	123	14	2	0.01	1	1	2.7	15	0.01
KL24-09	519	521.5	0.0021		21	0.06	0.1	47	44	13	3	0.01	1	0.5	1.8	13	0.01
KL24-09	521.5	525	0.0016		16	0.04	0.1	60	28	15	1	0.01	1	0.01	1.2	22	0.01
KL24-09	525	528	0.0014		14	0.03	0.1	82	41	12	2	0.01	1	0.5	1.7	20	0.01
KL24-09	528	531	0.0036		36	0.08	0.8	234	229	26	3	0.01	1	1.6	3.8	23	0.01
KL24-09	531	534	0.0043		43	0.16	1.7	382	216	55	5	0.01	1	4.8	8.0	41	0.01
KL24-09	534	537	0.0015		15	0.09	0.8	227	162	17	2	0.01	1	3.3	2.2	18	0.01
KL24-09	537	540	0.002		20	0.11	0.1	170	176	16	2	0.01	1	1.3	1.2	18	0.01
KL24-09	540	543	0.0081		81	0.12	0.9	340	360	31	4	0.01	1	1.8	2.9	16	0.01
KL24-09	543	546	0.0025		25	0.04	0.1	79	95	13	2	1	1	1	1.8	13	0.01
KL24-09	546	549	0.002		20	0.04	0.6	151	220	12	1	0.01	1	1	1.0	11	0.01
KL24-09	549	553	0.0021		21	0.06	0.7	247	273	10	2	0.01	1	0.9	1.0	12	0.01
KL24-09	553	555	0.0126		126	0.06	1.8	620	620	40	36	12	11	4.3	6.3	10	0.01
KL24-09	555	558	0.0063		63	0.07	5.7	1060	1320	19	2	0.01	1	2.7	2.3	11	0.01
KL24-09	558	560	0.0027		27	0.08	20.8	1350	2250	29	1	0.01	1	7.5	10.2	17	0.12
KL24-09	560	563	0.0029		29	0.09	16.3	830	1310	25	2	0.01	1	6.5	5.3	13	0.12
KL24-09	563	566	0.0052		52	0.08	11	830	1160	26	1	0.01	1	5.8	3.5	12	0.01
KL24-09	566	570	0.0017		17	0.09	6.1	690	910	18	1	0.01	1	4.3	3.2	14	0.01
KL24-09	570	573	0.0047		47	0.15	40	1580	820	45	1	0.01	1	11.8	3.4	20	0.15
KL24-09	573	576	0.0043		43	0.17	41	1480	810	46	2	0.01	1	13.8	6.1	25	0.17
KL24-09	576	577.7	0.0083		83	0.14	8.3	1180	820	40	3	0.01	1	5	7.5	18	0.01
KL24-10	0	2.6	0.0047		47	0.06	0.1	19	16	3	1	0.01	1	0.7	0.5	27	0.01
KL24-10	2.6	5.6	0.0036		36	0.07	0.1	35	23	1	1	0.01	1	0.8	1.4	29	0.01
KL24-10	5.6	8.6	0.0042		42	0.03	0.6	460	770	3	5	0.01	1	0.7	2.1	23	0.01
KL24-10	8.6	11.6	0.0014		14	0.02	0.8	131	52	16	2	0.01	1	1.4	3.0	21	0.01
KL24-10	11.6	14.6	0.004		40	0.02	0.1	226	113	14	1	0.01	1	1.5	3.3	30	0.01
KL24-10	14.6	17.6	0.0021		21	0.02	0.1	29	31	7	1	0.01	1	0.9	2.8	22	0.01
KL24-10	17.6	20.6	0.003		30	0.01	0.1	22	56	6	1	0.01	1	0.7	1.6	10	0.01
KL24-10	20.6	23.6	0.0078		78	0.03	0.1	40	46	9	1	0.01	1	1.6	1.6	25	0.01
KL24-10	23.6	26.6	0.0011		11	0.01	0.1	71	385	24	1	0.01	1	1	1.8	24	0.01
KL24-10	26.6	29.6	0.0021		21	0.06	0.1	58	60	17	1	0.01	1	0.9	4.7	37	0.01
KL24-10	29.6	32.6	0.0034		34	0.03	0.7	37	14	8	1	0.01	1	0.9	3.4	92	0.01
KL24-10	32.6	35.6	0.0066		66	0.11	0.1	45	148	12	1	1	2	1.4	15.4	141	0.01
KL24-10	35.6	38.6	0.0019		19	0.06	0.1	83	54	21	1	0.01	4	1.2	3.8	63	0.01
KL24-10	38.6	41.6	0.0035		35	0.02	4.5	138	126	15	1	0.01	1	2	3.6	46	0.01
KL24-10	41.6	44.6	0.0062		62	0.02	15.6	510	640	17	6	4	1	7.1	18.6	16	0.01
KL24-10	44.6	47.3	0.0183		183	0.04	27.5	1750	3030	8	15	24	1	10.8	19.0	31	0.01
KL24-10	47.3	48.5	0.0184		184	0.04	26.7	1650	2940	8	16	28	1	10.3	19.0	28	0.01
KL24-10	48.5	51.5	0.0025		25	0.01	0.8	117	132	4	12	1	1	0.5	3.8	260	0.01
KL24-10	51.5	53.6	0.0266		266	0.05	0.9	146	136	12	2	3	1	1.9	4.3	92	0.01
KL24-10	53.6	56.6	0.0268		268	0.04	0.8	150	143	13	3	2	1	1.5	4.2	114	0.01
KL24-10	56.6	59.3	0.0048		48	0.01	0.1	170	130	3	2	1	1	1.2	1.7	54	0.01
KL24-10	59.3	62.4	0.0021		21	0.01	0.1	49	43	4	7	0.01	1	1	1.0	109	0.01
KL24-10	62.4	65.5	0.0019		19	0.01	0.1	336	235	8	1	2	1	2	2.7	89	0.01
KL24-10	65.5	68.6	0.0028		28	0.02	1.4	260	261	5	2	13	1	1.7	3.7	66	0.01
KL24-10	68.6	71.6	0.75	7500	0.44	1.3	87	15	0.01	70	1	9	0.4	3.6	55	0.01	
KL24-10	71.6	74.3	0.0041		41	0.01	0.1	224	141	9	1	1	1	1.4	2.5	120	0.01
KL24-10	74.3	77.4	0.0028		28	0.01	0.1	252	84	4	4	2	1	0.7	1.2	119	0.01
KL24-10	77.4	80.5	0.0036		36	0.01	0.1	147	162	4	11	2	1	1.2	2.0	109	0.01
KL24-10	80.5	83.6	0.0025		25	0.01	0.1	133	148	6	1	1	1	1	1.1	37	0.01
KL24-10	83.6	85.2	0.0027		27	0.02	0.9	450	540	11	11	2	1	1.8	3.2	80	0.01
KL24-10	85.2	87.9	0.0042		42	0.01	0.1	307	140	14	26	2	1	1.3	2.9	58	0.01
KL24-10	87.9	89.3	0.0015		15	0.01	0.1	162	106	7	11	0.01	1	0.3	1.0	35	0.01
KL24-10	89.3	91.9	0.0025		25	0.01	1.8	127	150	19	14	0.01	1	2	1.2	12	0.01
KL24-10	91.9	95	0.0032		32	0.01	0.1	232	134	7	45	0.01	1	1.4	1.1	24	0.01
KL24-10	95	97.5	0.0067		67	0.01	1.5	173	156	17	19	3	1	3.4	6.6	66	0.01
KL24-10	97.5	99.2	0.0043		43	0.01	0.9	194	157	13	22	1	1	1.5	3.7	34	0.01
KL24-10	99.2	101.6	0.0137		137	0.01	10.8	276	770	17	7	0.01	1	24.8	2.4	21	0.01
KL24-10	101.6	104.6	0.0041		41	0.01	2.4	132	200	18	6	0.01	1	3.2	0.6	13	0.01
KL24-10	104.6	106.8	0.0021		21	0.01	1.5	153	500	8	4	0.01	1	1.4	1.3	16	0.01
KL24-10	106.8	109.3	0.0023		23	0.01	1.2	164	570	4	5	0.01	1	1.2	1.5	17	0.01
KL24-10	109.3	112	0.0016		16	0.01	0.6	173	303	3	2	0.01	1	0.9	2.6	21	0.01
KL24-10	113	115	0.0021		21	0.01	1.3	172	274	12	3	0.01	1	2.3	1.6	17	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL24-10	115	117.4	0.0029		29	0.01	0.1	112	312	19	3	0.01	1	0.6	1.1	15	0.01
KL24-10	117.4	119.1	0.0026		26	0.01	0.1	98	600	27	8	0.01	1	0.9	2.0	27	0.01
KL24-10	119.1	122	0.0112		112	0.1	1.5	530	870	190	11	0.01	1	4.8	3.5	18	0.18
KL24-10	122	124.9	0.0024		24	0.05	0.1	219	271	760	14	1	1	9.5	5.4	17	0.24
KL24-10	124.9	127	0.0027		27	0.04	1.4	510	810	49	2	1	1	4.1	2.9	20	1
KL24-10	127	128.6	0.0032		32	0.01	0.1	137	201	22	1	0.01	1	0.6	5.0	22	0.01
KL24-10	128.6	131.6	0.0027		27	0.01	0.1	268	400	30	1	0.01	1	2	4.3	21	0.42
KL24-10	131.6	134.6	0.0018		18	0.01	1	371	670	47	3	2	1	0.8	2.9	22	0.27
KL24-10	134.6	137.6	0.0015		15	0.01	0.1	106	363	33	1	0.01	1	0.9	1.4	20	0.01
KL24-10	137.6	140.6	0.0016		16	0.01	0.1	137	580	5	1	0.01	1	0.9	0.7	16	0.01
KL24-10	140.6	143.6	0.0076		76	0.01	0.8	640	590	26	3	0.01	1	2	0.8	24	0.01
KL24-10	143.6	146.6	0.0026		26	0.02	0.1	234	243	27	23	0.01	1	0.6	1.1	26	0.01
KL24-10	146.6	149.6	0.048		480	0.09	2.9	1040	1570	24	19	0.01	3	2.4	4.5	30	0.01
KL24-10	149.6	152.6	0.112		1120	0.3	3.6	1400	1340	1200	31	2	3	12	7.8	19	0.11
KL24-10	152.6	155.4	0.0203		203	0.05	1.1	650	840	27	19	1	1	1.3	2.2	27	0.01
KL24-10	155.4	158.1	0.0039		39	0.03	1	570	930	33	12	0.01	1	2.7	3.6	15	0.01
KL24-10	158.1	161.1	0.002		20	0.01	0.8	402	550	9	5	0.01	1	1	1.8	9	0.01
KL24-10	161.1	164.2	0.0023		23	0.01	0.8	430	590	12	4	0.01	1	1.1	1.8	12	0.01
KL24-10	164.2	167.3	0.0021		21	0.01	0.1	198	152	5	7	0.01	1	0.5	1.6	8	0.01
KL24-10	167.3	170.4	0.003		30	0.01	0.1	208	490	6	16	0.01	1	1	2.2	9	0.01
KL24-10	170.4	173.5	0.0015		15	0.01	0.1	269	630	5	19	0.01	1	1	2.1	14	0.01
KL24-10	173.5	176.1	0.002		20	0.01	0.1	322	490	2	6	0.01	1	0.7	3.0	15	0.01
KL24-10	176.1	179.2	0.0021		21	0.01	0.9	1120	1590	3	8	0.01	1	1	2.6	13	0.01
KL24-10	179.2	181.1	0.0024		24	0.01	0.1	232	408	1	1	0.01	1	0.7	1.3	13	0.01
KL24-10	181.1	182.6	0.0026		26	0.01	0.1	160	274	1	5	0.01	1	0.4	1.1	14	0.01
KL24-10	182.6	184.9	0.0096		96	0.02	0.8	500	308	20	5	0.01	1	1	2.1	15	0.01
KL24-10	184.9	188	0.0106		106	0.01	0.1	417	343	5	8	0.01	1	1	1.8	11	0.01
KL24-10	188	191	0.0045		45	0.02	2	480	1120	10	3	0.01	1	1.5	4.3	15	0.01
KL24-10	191	192.7	0.004		40	0.01	0.5	640	336	11	4	1	1	1.3	1.7	68	0.01
KL24-10	192.7	194.6	0.0028		28	0.01	1.8	2740	990	2	3	0.01	1	1.8	4.3	8	0.01
KL24-10	194.6	197.6	0.0025		25	0.01	0.5	560	399	5	1	0.01	1	1	3.1	7	0.01
KL24-10	197.6	200.6	0.0028		28	0.01	0.1	106	107	3	11	0.01	1	0.3	1.5	20	0.01
KL24-10	200.6	203.3	0.0021		21	0.01	0.1	113	126	3	9	0.01	1	0.6	2.0	14	0.01
KL24-10	203.3	206.2	0.0338		338	0.08	2.5	1350	850	54	18	0.01	1	3	4.3	26	0.01
KL24-10	206.2	209.3	0.0024		24	0.01	0.6	117	114	3	8	0.01	1	0.4	2.5	15	0.01
KL24-10	209.3	212.4	0.0074		74	0.02	4.2	2100	2130	15	4	0.01	1	3.8	9.3	14	0.01
KL24-10	212.4	214	0.006		60	0.01	0.8	90	410	6	10	0.01	1	0.7	1.7	26	0.01
KL24-10	214	216.6	0.0174		174	0.12	5.8	3380	2560	31	76	6	3	2.7	12.5	53	0.01
KL24-10	216.6	218.6	0.0028		28	0.01	0.7	420	550	3	14	0.01	1	0.7	1.5	20	0.01
KL24-10	218.6	221.6	0.0031		31	0.01	0.5	287	300	3	7	0.01	1	0.6	1.8	18	0.01
KL24-10	221.6	224.6	0.0015		15	0.01	0.1	420	360	3	12	0.01	1	0.5	2.5	16	0.01
KL24-10	224.6	227.6	4.31	43100	1.47	3.5	365	131	0.01	13	3	24	0.01	18.8	35	0.01	
KL24-10	227.6	230.6	0.012		120	0.02	2	1910	2280	10	16	6	1	2.5	36.0	17	0.01
KL24-10	230.6	233.6	0.089		890	0.04	1.5	610	620	12	30	5	2	1.1	5.0	24	0.01
KL24-10	233.6	236.6	0.0181		181	0.03	0.8	1020	1070	18	10	1	3	1.1	2.8	23	0.01
KL24-10	236.6	239.6	0.0105		105	0.08	2.3	1630	510	23	133	30	2	1.2	8.5	15	0.01
KL24-10	239.6	242.6	0.33	3300	0.16	88	44400	32500	25	558	1090	15	10.5	193.0	42	0.01	
KL24-10	242.6	245.6	0.0118		118	0.17	1.3	299	175	10	2040	10	1	0.6	9.0	36	0.01
KL24-10	245.6	248.6	0.0242		242	0.26	1.8	680	254	16	1990	12	1	1	12.0	34	0.01
KL24-10	248.6	251.6	0.0215		215	0.03	1.1	640	138	9	138	26	1	0.5	4.3	43	0.01
KL24-10	251.6	254.6	2.36	23600	1.51	24.3	162000	301	14	78	272	100	0.7	135.0	38	0.01	
KL24-10	254.6	257.6	0.67	6700	1.17	15.1	100000	5360	8	498	228	48	2.5	158.0	25	0.01	
KL24-10	257.6	260.6	0.39	3900	2.99	35	77400	8820	49	53	1300	36	10.7	345.0	42	0.01	
KL24-10	260.6	263.6	0.2	2000	0.19	4.9	2150	790	6	1340	75	1	0.5	19.3	25	0.01	
KL24-10	263.6	266.6	0.116	1160	0.25	7.2	8300	590	21	550	306	12	0.4	29.4	16	0.01	
KL24-10	266.6	269.6	0.57	5700	6.95	77	18300	5400	16	229	1560	12	0.8	196.0	32	0.01	
KL24-10	269.6	272.6	0.15	1500	0.31	2.3	6100	174	13	207	39	5	0.2	16.5	14	0.01	
KL24-10	272.6	275.6	0.25	2500	0.3	3.8	4930	430	17	71	20	4	0.5	12.3	18	0.01	
KL24-10	275.6	278.6	0.28	2800	0.63	13.7	25900	2150	18	21	67	12	4.3	40.0	41	0.01	
KL24-10	278.6	281.6	0.421	4210	0.22	1.6	400	131	5	477	3	34	0.3	6.3	16	0.01	
KL24-10	281.6	284.6	0.338	3380	0.25	1.6	360	37	17	794	4	14	0.01	7.8	22	0.01	
KL24-10	284.6	287.6	0.064	640	0.06	0.1	126	35	45	165	2	2	0.01	2.0	25	0.01	
KL24-10	287.6	290.6	0.6	6000	0.37	3	3260	30	18	101	2	32	0.01	9.3	26	0.01	

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL24-10	290.6	293.6	1	10000	0.56	4.1	1100	40	8	45	4	36	0.01	11.5	14	0.01
KL24-10	293.6	296.6	0.63	6300	0.36	2.3	13800	21	6	46	3	52	0.2	19.0	19	0.01
KL24-10	296.6	299.6	0.63	6300	0.38	2.3	7200	24	6	401	2	16	0.01	13.3	22	0.01
KL24-10	299.6	302.6	0.88	8800	0.33	4.3	1570	12	4	25	3	149	0.2	11.5	15	0.01
KL24-10	302.6	304.6	0.87	8700	0.33	4.6	21900	15	14	93	3	218	0.7	15.0	15	0.01
KL24-10	304.6	307.4	0.92	9200	0.78	8.4	7000	212	6	12	24	86	0.4	19.5	19	0.01
KL24-10	307.4	308.6	0.385	3850	0.35	5.9	2890	138	5	12	48	56	0.5	7.0	17	0.01
KL24-10	308.6	311.6	2.78	27800	1.73	5.1	133	36	1	104	2	28	0.01	12.0	35	0.01
KL24-10	311.6	314.6	0.51	5100	0.22	4.7	10100	62	4	9	10	88	0.2	7.0	12	0.01
KL24-10	314.6	317.6	0.93	9300	0.83	9.3	1690	12	3	9	53	33	0.9	10.3	12	0.01
KL24-10	317.6	320.6	0.8	8000	0.91	6	710	21	2	5	40	51	0.01	8.3	14	0.01
KL24-10	320.6	323.6	0.56	5600	0.45	1.8	312	19	1	6	2	58	0.01	6.8	18	0.01
KL24-10	323.6	326.6	0.96	9600	0.69	2.1	310	7	1	16	4	52	0.01	11.0	16	0.01
KL24-10	326.6	329.6	0.8	8000	0.8	1.2	122	8	9	27	0.01	33	0.01	8.5	25	0.01
KL24-10	329.6	332.6	1.53	15300	1.36	1.9	510	15	2	147	0.01	42	0.01	16.5	26	0.01
KL24-10	332.6	335.6	0.29	2900	0.39	0.6	137	6	1	4	0.01	35	0.01	5.5	19	0.01
KL24-10	335.6	338.6	1.17	11700	0.96	1.3	223	7	3	3	0.01	24	0.01	10.5	44	0.01
KL24-10	338.6	341.6	0.69	6900	0.47	0.9	124	7	1	1	0.01	35	0.01	7.3	61	0.01
KL24-10	341.6	344.6	0.23	2300	0.24	2.6	6800	11	5	13	4	28	0.01	4.0	16	0.01
KL24-10	344.6	347.6	0.0022	22	0.01	0.6	276	213	2	13	0.01	1	0.7	1.3	13	0.01
KL24-10	347.6	350.6	0.97	9700	0.77	1.6	147	13	0.01	11	2	27	0.01	9.0	37	0.01
KL24-10	350.6	352.9	1.02	10200	0.75	1.8	165	10	1	131	2	23	0.01	8.5	87	0.01
KL24-10	352.9	354.5	0.7	7000	0.31	4.2	266	27	1	166	2	20	0.01	9.5	82	0.01
KL24-10	354.5	356.6	0.85	8500	0.77	3.8	620	11	3	860	4	21	0.6	7.3	58	0.01
KL24-10	356.6	359.6	0.76	7600	0.53	1.5	108	11	1	660	0.01	15	0.01	8.6	121	0.01
KL24-10	359.6	362.6	0.89	8900	0.53	1.4	63	11	0.01	59	0.01	11	0.01	6.5	84	0.01
KL24-10	362.6	365.6	0.62	6200	0.34	1.7	128	21	0.01	77	1	10	0.01	4.8	69	0.01
KL24-10	365.6	368.6	0.63	6300	0.44	1.4	225	21	1	89	0.01	13	0.01	6.3	86	0.01
KL24-10	368.6	371.6	0.75	7500	0.48	1.3	50	23	0.01	62	0.01	12	0.01	5.0	90	0.01
KL24-10	371.6	374.6	0.4	4000	0.17	1.1	42	12	1	14	0.01	6	0.01	4.0	113	0.01
KL24-10	374.6	377.6	0.7	7000	0.53	2.1	2010	460	2	50	3	7	0.6	5.3	116	0.01
KL24-10	377.6	380.6	0.43	4300	0.32	1	30	10	1	11	0.01	5	0.01	4.6	243	0.01
KL24-10	380.6	383.6	0.431	4310	0.19	1.3	59	18	1	17	0.01	7	0.01	7.9	147	0.01
KL24-10	383.6	386.6	0.53	5300	0.46	1.3	56	13	1	47	0.01	13	0.01	4.3	78	0.01
KL24-10	386.6	389.6	0.61	6100	0.43	1.2	54	11	0.01	52	0.01	13	0.01	4.8	69	0.01
KL24-10	389.6	392.6	0.69	6900	0.48	1.2	60	19	1	101	1	12	0.01	4.0	99	0.01
KL24-10	392.6	395.6	0.53	5300	0.4	1.7	65	15	0.01	34	1	11	0.01	4.3	72	0.01
KL24-10	395.6	398.6	0.78	7800	0.48	1.8	59	12	1	78	0.01	14	0.01	4.8	103	0.01
KL24-10	398.6	401.6	0.83	8300	0.5	1.6	65	10	0.01	132	0.01	13	0.01	4.5	78	0.01
KL24-10	401.6	404.6	0.65	6500	0.33	2	84	27	2	47	2	11	0.6	8.6	67	0.01
KL24-10	404.6	407.6	0.55	5500	0.24	1.1	57	16	9	43	0.01	10	0.01	4.3	95	0.01
KL24-10	407.6	410.6	0.65	6500	0.36	1.3	84	18	3	38	0.01	9	0.01	4.1	123	0.01
KL24-10	410.6	413.6	0.68	6800	0.55	1.3	106	26	1	70	0.01	8	0.5	3.8	80	0.01
KL24-10	413.6	416.6	0.93	9300	0.68	1.8	207	24	1	113	1	13	0.2	5.0	79	0.01
KL24-10	416.6	419.6	0.71	7100	0.5	1.4	71	21	0.01	93	0.01	9	0.01	4.6	78	0.01
KL24-10	419.6	422.6	0.52	5200	0.34	1.4	104	35	0.01	164	0.01	11	0.4	5.0	70	0.01
KL24-10	422.6	425.6	0.4	4000	0.28	1.5	78	48	2	96	1	10	0.2	6.3	74	0.01
KL24-10	425.6	428.6	0.518	5180	0.53	1.1	39	13	1	25	1	6	0.01	4.8	175	0.01
KL24-10	428.6	431.6	0.45	4500	0.36	1.3	36	11	1	74	0.01	12	0.01	5.8	72	0.01
KL24-10	431.6	434.6	0.61	6100	0.4	1.4	67	18	1	61	0.01	12	0.01	5.5	64	0.01
KL24-10	434.6	437.6	0.368	3680	0.27	0.9	33	8	3	56	0.01	8	0.01	3.0	152	0.01
KL24-10	437.6	440.6	0.435	4350	0.23	1	201	82	1	48	0.01	9	0.01	5.3	59	0.01
KL24-10	440.6	443.6	0.556	5560	0.24	1.6	54	25	6	37	1	8	0.5	6.1	125	0.01
KL24-10	443.6	446.6	0.722	7220	0.08	1.5	112	28	2	429	2	6	0.01	6.3	39	0.01
KL24-10	446.6	449.6	0.428	4280	0.2	1.1	49	21	2	22	1	5	0.2	3.3	200	0.01
KL24-10	449.6	452	0.722	7220	0.51	2.8	76	20	3	26	0.01	11	0.3	8.0	89	0.01
KL24-10	452	453.7	0.357	3570	0.23	1.4	65	22	1	160	0.01	12	0.2	9.3	65	0.01
KL24-10	453.7	455.6	0.64	6400	0.29	2.4	88	39	4	81	5	14	0.9	14.5	79	0.01
KL24-10	455.6	458.6	0.442	4420	0.29	2.2	76	25	1	192	2	12	0.3	8.0	67	0.01
KL24-10	458.6	461.6	0.8	8000	0.44	0.9	54	6	1	121	0.01	13	0.01	4.0	78	0.01
KL24-10	461.6	464.6	0.585	5850	0.25	1.7	46	13	2	30	1	7	0.01	4.5	238	0.01
KL24-10	464.6	467.6	1.49	14900	0.64	4.8	119	41	190	19	4	5	8	10.5	95	0.01
KL24-10	467.6	470.6	0.78	7800	0.75	2.5	161	42	10	15	4	4	0.9	5.7	71	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL24-10	470.6	473.6	0.75	7500	0.25	1.8	34	16	2	13	2	7	0.01	5.5	195	0.01
KL24-10	473.6	476.6	0.389	3890	0.26	1.1	48	14	1	12	0.01	7	0.01	5.5	145	0.01
KL24-10	476.6	479.6	0.408	4080	0.43	1	53	18	4	14	1	6	0.5	5.5	194	0.01
KL24-10	479.6	482.6	0.52	5200	0.5	0.8	47	13	1	12	1	7	0.01	4.7	170	0.01
KL24-10	482.6	485.6	1.09	10900	0.96	2.7	61	25	1	10	3	7	0.2	7.5	223	0.01
KL24-10	485.6	488.6	0.48	4800	0.48	1.1	51	15	2	10	1	7	0.4	3.9	169	0.01
KL24-10	488.6	491.6	0.366	3660	0.18	1	85	29	34	8	1	6	10.5	4.3	166	0.01
KL24-10	491.6	494.6	0.429	4290	0.3	1.1	52	18	2	12	1	8	0.4	3.8	179	0.01
KL24-10	494.6	497.6	0.395	3950	0.4	0.8	57	16	2	13	1	5	0.3	3.5	152	0.01
KL24-10	497.6	500.6	0.37	3700	0.32	0.9	41	10	1	21	0.01	6	0.01	2.3	188	0.01
KL24-10	500.6	503.6	0.382	3820	0.4	1	25	9	1	8	0.01	5	0.01	3.3	182	0.01
KL24-10	503.6	506.6	0.412	4120	0.39	0.9	63	20	2	13	2	5	0.6	4.3	136	0.01
KL24-10	506.6	509.6	0.299	2990	0.27	1.5	105	91	8	9	5	4	6.8	7.7	186	0.01
KL24-10	509.6	512.6	0.28	2800	0.3	0.7	82	35	1	12	1	4	0.3	1.5	217	0.01
KL24-10	512.6	515.6	0.56	5600	0.17	1.5	125	76	2	32	3	6	1.4	3.3	108	0.01
KL24-10	515.6	518.6	0.605	6050	0.33	1.6	40	22	2	15	2	6	0.6	3.9	230	0.01
KL24-10	518.6	521.6	0.546	5460	0.45	1.4	62	28	1	17	1	5	0.01	3.5	189	0.01
KL24-10	521.6	524.6	0.71	7100	0.39	1.4	71	26	15	16	2	5	0.4	2.3	215	0.01
KL24-10	524.6	527.6	0.488	4880	0.54	1.2	82	26	10	45	1	7	0.3	3.3	170	0.01
KL24-10	527.6	530.6	0.517	5170	0.56	1.1	35	13	4	10	0.01	5	0.2	2.3	92	0.01
KL24-10	530.6	533.6	1.85	18500	0.32	2.8	172	49	11	154	2	19	0.4	13.5	54	0.01
KL24-10	533.6	536.6	0.605	6050	0.2	1.8	125	36	2	20	3	4	0.2	2.3	203	0.01
KL24-10	536.6	539.6	0.446	4460	0.5	1.1	48	14	4	9	1	3	0.01	3.0	202	0.01
KL24-10	539.6	542.6	0.24	2400	0.21	0.8	95	48	1	19	1	6	0.01	3.0	111	0.01
KL24-10	542.6	545.6	0.474	4740	0.4	1.2	45	15	4	22	1	5	0.01	4.0	195	0.01
KL24-10	545.6	548.6	0.6	6000	0.31	1.9	37	13	5	24	1	6	0.01	6.5	188	0.01
KL24-10	548.6	551.6	0.91	9100	0.53	2.6	41	15	8	18	1	8	0.2	6.0	131	0.01
KL24-10	551.6	554.6	0.67	6700	0.36	1.9	66	26	4	40	1	6	0.01	4.7	214	0.01
KL24-10	554.6	557.6	0.451	4510	0.47	1	44	20	2	38	1	6	0.01	4.3	168	0.01
KL24-10	557.6	560.6	0.418	4180	0.37	1.2	32	11	1	15	1	5	0.01	4.3	162	0.01
KL24-10	560.6	563.6	0.488	4880	0.5	1.1	39	12	2	28	1	5	0.01	5.3	116	0.01
KL24-10	563.6	566.6	0.456	4560	0.54	0.9	76	15	8	60	1	5	0.01	5.1	166	0.01
KL24-10	566.6	569.6	0.493	4930	0.45	1	98	22	7	58	1	8	0.01	4.5	175	0.01
KL24-10	569.6	572.6	0.418	4180	0.2	1.1	54	12	1	35	1	7	0.01	4.5	80	0.01
KL24-10	572.6	575.6	0.575	5750	0.36	0.9	70	16	1	71	1	10	0.2	4.3	86	0.01
KL24-10	575.6	578.6	0.448	4480	0.24	1	41	18	0.01	21	0.01	6	0.01	4.1	97	0.01
KL24-10	578.6	581.6	0.24	2400	0.15	0.9	37	20	2	24	1	5	0.01	2.8	113	0.01
KL24-10	581.6	584.6	0.375	3750	0.25	1.2	140	54	1	17	2	5	0.01	4.0	103	0.01
KL24-10	584.6	587.6	0.434	4340	0.24	1.1	68	27	2	18	1	5	0.4	4.5	104	0.01
KL24-10	587.6	590.6	0.342	3420	0.25	1	63	24	3	22	1	6	0.2	4.3	99	0.01
KL24-10	590.6	593.6	0.409	4090	0.18	1.2	47	16	5	23	1	5	0.5	4.5	185	0.01
KL24-10	593.6	596.6	0.425	4250	0.35	0.8	46	22	2	14	1	4	0.01	3.2	205	0.01
KL24-10	596.6	599.6	0.423	4230	0.21	1	50	17	3	17	1	5	0.2	3.5	182	0.01
KL24-10	599.6	602.6	0.346	3460	0.11	1.2	116	32	3	63	1	5	0.2	3.3	185	0.01
KL24-10	602.6	605.6	0.437	4370	0.21	1.4	75	38	0.01	24	0.01	5	0.3	4.3	114	0.01
KL24-10	605.6	607.5	0.644	6440	0.67	1.2	64	14	1	80	1	7	0.01	4.3	78	0.01
KL24-10	607.5	608.6	0.76	7600	0.48	1.2	63	12	0.01	100	0.01	11	0.01	6.3	74	0.01
KL24-10	608.6	611.6	0.389	3890	0.15	1.3	153	22	1	26	1	11	0.01	5.5	56	0.01
KL24-10	611.6	614.6	0.527	5270	0.36	1.2	790	166	1	48	2	8	0.3	5.5	71	0.01
KL24-10	614.6	617.6	0.435	4350	0.35	1	37	16	1	25	1	5	0.01	4.3	186	0.01
KL24-10	617.6	620.6	0.48	4800	0.24	1	61	12	0.01	18	1	8	0.01	2.8	142	0.01
KL24-10	620.6	623.5	0.575	5750	0.49	0.7	74	26	1	29	1	12	0.2	5.3	72	0.01
KL24-10	623.5	626.6	0.8	8000	0.32	2.5	93	61	8	25	3	12	0.8	8.3	55	0.01
KL24-10	626.6	629.6	0.477	4770	0.65	1.2	31	8	1	12	1	4	0.01	3.2	213	0.01
KL24-10	629.6	632.6	0.281	2810	0.13	0.9	36	7	0.01	119	0.01	6	0.01	2.5	206	0.01
KL24-10	632.6	635.6	0.378	3780	0.17	0.9	30	9	0.01	13	0.01	7	0.3	4.0	197	0.01
KL24-10	635.6	638.1	0.324	3240	0.11	1	34	9	1	10	0.01	6	0.4	2.5	129	0.01
KL24-10	638.1	641.1	0.352	3520	0.21	0.8	26	8	0.01	14	0.01	4	0.01	2.8	217	0.01
KL24-10	641.1	644.2	0.517	5170	0.33	1.2	27	13	1	21	0.01	8	0.01	4.0	216	0.01
KL24-10	644.2	647.3	0.346	3460	0.24	0.8	41	13	1	20	1	6	0.01	2.3	166	0.01
KL24-10	647.3	650.1	0.252	2520	0.14	0.6	28	10	0.01	9	0.01	4	0.01	2.0	177	0.01
KL24-10	650.1	653.2	0.287	2870	0.18	0.8	28	10	0.01	13	0.01	4	0.01	2.5	184	0.01
KL24-10	653.2	656.3	0.22	2200	0.12	0.6	26	10	0.01	9	0.01	3	0.01	1.8	156	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL24-11	234.5	237.5	0.001	10	0.01	1.3	540	1070	3	4	0.01	1	1.6	2.8	14	0.01
KL24-11	237.5	240.5	0.0015	15	0.01	0.8	276	374	4	7	0.01	1	0.9	2.3	19	0.01
KL24-11	240.5	243.5	0.0032	32	0.01	1.8	620	920	13	12	0.01	1	2.2	3.5	22	0.01
KL24-11	243.5	246.5	0.0018	18	0.01	2.1	261	450	8	11	1	1	1	7.3	17	0.01
KL24-11	246.5	249.5	0.0284	284	0.06	1.7	1500	690	16	9	5	1	1.7	3.8	15	0.01
KL24-11	249.5	252.5	0.0026	26	0.01	0.1	109	85	4	6	0.01	1	0.4	0.8	11	0.01
KL24-11	252.5	255.5	0.0194	194	0.02	0.1	1220	287	11	36	0.01	1	1.1	3.5	20	0.01
KL24-11	255.5	258.5	0.0193	193	0.02	0.1	331	378	15	21	3	1	0.7	4.5	15	0.01
KL24-11	258.5	261.5	0.0405	405	0.05	0.9	1350	240	24	285	2	1	1	7.3	23	0.01
KL24-11	261.5	264.5	0.01	100	0.03	1.8	630	356	9	47	1	1	1.3	2.5	19	0.01
KL24-11	264.5	267.5	0.0042	42	0.06	5	1260	1100	8	7	0.01	1	2.6	4.5	18	0.01
KL24-11	267.5	270.5	0.0054	54	0.16	38	5300	7600	17	7	0.01	1	9.1	38.5	18	0.01
KL24-11	270.5	273.5	0.0056	56	0.03	1.4	560	550	11	13	0.01	1	1.9	3.5	27	0.01
KL24-11	273.5	276.5	0.0038	38	0.01	2.1	1630	1850	9	10	0.01	1	3.1	5.3	16	0.01
KL24-11	276.5	279.5	0.0108	108	0.01	2.3	2080	3250	9	15	1	1	4.2	10.0	24	0.01
KL24-11	279.5	282.5	0.0064	64	0.01	0.8	780	890	4	12	3	1	1.1	3.6	18	0.01
KL24-11	282.5	285.5	0.006	60	0.01	1.5	1650	920	7	24	2	1	1.3	4.0	19	0.01
KL24-11	285.5	288.5	0.0068	68	0.02	0.1	397	130	9	15	0.01	1	0.6	2.3	17	0.01
KL24-11	288.5	291	0.0043	43	0.02	0.1	238	141	3	14	1	1	0.4	1.3	11	0.01
KL24-11	291	294	0.0139	139	0.02	2.2	860	450	9	8	26	1	0.6	5.0	18	0.01
KL24-11	294	296.6	0.0238	238	0.65	1.2	1030	160	27	10	5	2	0.9	2.8	32	0.01
KL24-11	296.6	298.2	0.0137	137	0.08	0.1	400	36	18	14	2	1	0.3	1.3	11	0.01
KL24-11	298.2	300.6	0.063	630	0.45	1.3	3960	121	12	11	24	6	0.5	6.3	18	0.01
KL24-11	300.6	303.6	0.0074	74	0.01	0.1	289	163	8	6	1	1	0.3	1.3	14	0.01
KL24-11	303.6	306.5	0.162	1620	0.21	1.3	3350	160	21	43	20	6	1.9	13.3	36	0.01
KL24-11	306.5	309.5	0.0326	326	0.26	0.1	81	47	7	213	23	1	0.2	2.2	58	0.01
KL24-11	309.5	312.5	0.0192	192	0.06	0.1	168	28	2	440	2	2	1	0.8	78	0.01
KL24-11	312.5	315.5	0.123	1230	0.18	0.6	203	191	4	1030	4	6	2.6	7.0	105	0.01
KL24-11	315.5	318.5	0.203	2030	1.56	3	318	43	5	307	5	4	0.3	9.3	135	0.01
KL24-11	318.5	321.5	0.098	980	0.2	0.1	140	64	15	368	15	3	0.9	6.8	112	0.01
KL24-11	321.5	324.5	0.77	7700	1.32	5.4	3900	70	19	71	85	15	1.2	26.4	73	0.01
KL24-11	324.5	327.5	0.45	4500	0.66	6.7	5700	75	8	206	590	7	1	75.5	44	0.01
KL24-11	327.5	330.5	0.231	2310	0.48	1.1	182	49	8	212	240	2	0.4	20.4	43	0.01
KL24-11	330.5	333.5	0.68	6800	1.62	3.1	1080	70	8	158	320	7	0.6	23.8	33	0.01
KL24-11	333.5	336.5	0.23	2300	0.48	1.1	217	45	14	82	53	4	1.1	16.5	42	0.01
KL24-11	336.5	339.5	1.35	13500	2.28	6	8000	82	10	48	305	22	0.01	37.0	36	0.01
KL24-11	339.5	342.5	0.51	5100	0.39	2.1	5400	24	3	49	36	10	0.01	18.8	28	0.01
KL24-11	342.5	345.5	0.7	7000	0.41	2.4	4600	32	4	77	5	25	0.01	19.2	63	0.01
KL24-11	345.5	348.5	1.17	11700	0.72	2.9	1180	35	6	198	6	23	0.2	15.5	42	0.01
KL24-11	348.5	351.5	0.97	9700	0.72	2.4	430	23	6	213	6	22	0.2	18.0	46	0.01
KL24-11	351.5	354.5	0.501	5010	0.59	6.1	740	78	4	140	78	25	0.01	32.4	44	0.01
KL24-11	354.5	357.5	0.23	2300	0.36	3.7	750	51	8	1620	6	5	0.01	35.3	63	0.01
KL24-11	357.5	360.5	0.193	1930	0.18	0.7	53	20	9	1520	3	3	0.01	7.3	51	0.01
KL24-11	360.5	363.5	0.325	3250	3.07	1.8	239	32	12	235	28	22	0.01	21.5	95	0.01
KL24-11	363.5	366.5	0.93	9300	0.49	2.3	1290	31	4	70	5	26	0.01	24.8	61	0.01
KL24-11	366.5	369.5	0.5	5000	0.39	3	36000	24	11	24	16	91	1	34.5	36	0.01
KL24-11	369.5	372.5	0.2	2000	0.22	4.1	4700	238	12	8	26	20	1.5	11.5	26	0.01
KL24-11	372.5	375.5	0.6	6000	0.54	11.5	22600	620	16	7	16	34	0.8	19.5	46	0.01
KL24-11	375.5	377.6	0.123	1230	0.25	5.4	1980	700	17	7	11	4	0.6	8.5	35	0.01
KL24-11	377.6	379.5	0.074	740	0.2	3.4	2730	2150	3	6	9	10	0.7	10.8	21	0.01
KL24-11	379.5	381.5	1.41	14100	1.08	5.4	600	26	3	7	18	38	2.2	19.5	42	0.01
KL24-11	381.5	384.5	0.76	7600	0.81	1.1	132	41	2	13	1	17	0.01	8.5	46	0.01
KL24-11	384.5	387.5	0.97	9700	0.72	1.2	640	10	0.01	17	2	27	0.01	13.3	36	0.01
KL24-11	387.5	390.5	2.26	22600	1.94	3.1	129	23	0.01	13	2	25	0.01	14.0	29	0.01
KL24-11	390.5	393.5	1.62	16200	2.06	3.3	116	16	5	14	1	31	0.01	20.2	81	0.01
KL24-11	393.5	396.5	1.35	13500	1.8	1.9	156	21	41	32	0.01	37	0.3	24.5	70	0.2
KL24-11	396.5	399.5	1.07	10700	0.76	1.3	281	14	2	179	0.01	24	0.01	11.0	76	0.01
KL24-11	399.5	402.5	0.163	1630	0.16	0.1	63	13	2	19	1	13	0.4	4.8	74	0.01
KL24-11	402.5	405.5	2.06	20600	0.53	7.2	125	128	210	15	8	17	6.8	43.0	208	0.12
KL24-11	405.5	408.5	3.26	32600	1.83	7.5	209	115	48	14	6	12	9.3	27.5	272	0.01
KL24-11	408.5	411.5	2.35	23500	1.62	7	81	50	24	13	5	17	10.3	34.5	190	0.01
KL24-11	411.5	414.5	0.95	9500	0.49	1.2	67	13	10	30	1	14	0.2	5.3	83	0.01
KL24-11	414.5	416.2	0.62	6200	0.37	1	50	20	12	143	1	9	0.2	5.5	123	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL24-11	416.2	418.2	0.29	2900	0.15	0.1	34	8	5	136	1	9	0.2	6.5	110	0.01
KL24-11	418.2	420	0.448	4480	0.35	0.8	32	10	4	79	1	10	0.01	6.5	96	0.01
KL24-11	420	421.5	0.82	8200	0.57	1.3	32	8	4	81	0.01	8	0.01	8.0	121	0.01
KL24-11	421.5	423.5	0.434	4340	0.25	0.8	35	17	5	102	2	9	0.4	15.7	141	0.01
KL24-11	423.5	426.5	0.69	6900	0.39	0.9	53	17	9	32	3	10	1	12.3	168	0.01
KL24-11	426.5	429.5	0.81	8100	0.87	1.2	64	12	4	44	1	14	0.3	8.0	143	0.01
KL24-11	429.5	432.5	0.92	9200	1.08	1.2	53	9	4	24	1	9	0.01	7.8	110	0.01
KL24-11	432.5	435.5	0.362	3620	0.39	0.1	33	12	3	69	1	6	0.01	5.0	108	0.01
KL24-11	435.5	438.5	0.58	5800	0.38	0.9	53	19	3	54	0.01	10	0.2	7.8	101	0.01
KL24-11	438.5	441.5	0.64	6400	0.59	1.3	88	26	8	53	1	10	0.7	10.6	135	0.01
KL24-11	441.5	444.5														
KL24-11	444.5	447.5														
KL24-11	447.5	450.5														
KL24-11	450.5	453.5														
KL24-11	453.5	456.5														
KL24-11	456.5	459.5														
KL24-11	459.5	462.5														
KL24-11	462.5	465.5														
KL24-11	465.5	468.5														
KL24-11	468.5	471.5														
KL24-11	471.5	474.5														
KL24-11	474.5	477.5														
KL24-11	477.5	480.5														
KL24-11	480.5	483.5														
KL24-11	483.5	486.5														
KL24-11	486.5	489.5														
KL24-11	489.5	492.5														
KL24-11	492.5	495.5														
KL24-11	495.5	498.5														
KL24-11	498.5	501.5														
KL24-11	501.5	504.5														
KL24-11	504.5	507.5														
KL24-11	507.5	510.5														
KL24-11	510.5	513.5														
KL24-11	513.5	514.5														
KL24-11	514.5	516.5														
KL24-11	516.5	517.5														
KL24-11	517.5	519.5														
KL24-11	519.5	522.5														
KL24-11	522.5	525.5														
KL24-11	525.5	528.5														
KL24-11	528.5	531.5														
KL24-11	531.5	540.5														
KL24-11	540.5	542.5														
KL24-11	542.5	544.7														
KL24-11	544.7	546.5														
KL24-11	546.5	549.5														
KL24-11	549.5	552.5														
KL24-11	552.5	555.5														
KL24-11	555.5	558.5														
KL24-11	558.5	561.5														
KL24-11	561.5	564.5														
KL24-11	564.5	585.5														
KL24-11	585.5	606.5														
KL24-11	606.5	648.5														
KL26-01	0	2.9	0.0028	28	0.01	0.1	84	51	6	3	0.01	1	1.5	1.3	20	0.01
KL26-01	2.9	5.9	0.0013	13	0.01	0.1	26	16	8	1	0.01	1	0.3	1.5	23	0.01
KL26-01	5.9	8.9	0.0012	12	0.01	0.1	18	10	5	2	0.01	2	0.01	0.0	35	0.01
KL26-01	8.9	11.9	0.0014	14	0.01	0.1	25	18	5	2	0.01	2	0.01	0.0	28	0.01
KL26-01	11.9	14.9	0.001	10	0.01	0.1	41	16	6	2	0.01	1	0.01	0.6	30	0.01
KL26-01	14.9	17.9	0.0009	9	0.01	0.1	21	13	4	1	0.01	1	0.01	0.0	30	0.01
KL26-01	17.9	20.9	0.0007	7	0.01	0.1	40	13	4	1	0.01	1	0.01	0.6	25	0.01
KL26-01	20.9	23.9	0.0007	7	0.01	0.1	30	20	3	1	0.01	1	0.01	0.0	48	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL26-01	23.9	26.9	0.0013		13	0.01	1.2	77	880	11	2	0.01	1	2.5	2.8	71	0.01
KL26-01	26.9	29.9	0.0012		12	0.01	0.1	53	57	14	4	0.01	4	1.1	1.5	110	0.01
KL26-01	29.9	35.9	0.0098		98	0.1	7.2	2310	1800	21	3	1	1	4.7	9.1	52	0.01
KL26-01	35.9	40.3	0.0082		82	0.06	9.2	750	8300	56	16	4	1	7.3	17.0	28	0.01
KL26-01	40.3	43.4	0.0019		19	0.04	1.5	103	2950	10	9	0.01	1	1.8	3.6	116	0.01
KL26-01	43.4	46.4	0.0023		23	0.04	1.1	121	2140	18	8	0.01	1	3.4	1.0	93	0.01
KL26-01	46.4	49.4	0.002		20	0.03	0.7	118	1320	11	6	0.01	1	1.5	0.6	93	0.01
KL26-01	49.4	52.4	0.0012		12	0.01	1.1	86	1610	15	14	0.01	1	4.8	0.0	73	0.01
KL26-01	52.4	53.9	0.001		10	0.01	1.2	130	2020	10	8	0.01	1	2.9	0.9	100	0.01
KL26-01	53.9	56.9	0.001		10	0.01	1.4	136	1110	12	6	0.01	1	2.1	0.0	70	0.01
KL26-01	56.9	58.4	0.0007		7	0.02	1.3	129	800	13	5	0.01	1	2.7	0.0	64	0.01
KL26-01	58.4	61.4	0.001		10	0.01	0.9	92	178	10	6	0.01	1	1.8	0.0	51	0.01
KL26-01	61.4	64.4	0.0011		11	0.03	1.1	99	351	17	13	1	1	1.8	0.0	42	0.01
KL26-01	64.4	67.4	0.0025		25	0.01	4.6	3390	2920	38	6	0.01	1	4.9	11.6	27	0.01
KL26-01	67.4	69.5	0.0013		13	0.02	1.1	198	450	38	5	0.01	1	1.7	0.0	31	0.01
KL26-01	69.5	71.9	0.0031		31	0.08	2.6	190	820	36	8	0.01	1	4.7	0.8	36	0.01
KL26-01	71.9	73.7	0.0034		34	0.01	5.2	1960	3820	4	7	1	1	4.3	2.4	25	0.01
KL26-01	73.7	76.4	0.0025		25	0.01	7.2	109	1800	12	5	9	1	1.3	1.7	19	0.01
KL26-01	76.4	79.4	0.0018		18	0.01	4.6	70	920	16	11	7	1	0.7	1.4	16	0.01
KL26-01	79.4	81.9	0.001		10	0.04	0.1	129	130	5	6	0.01	1	0.01	1.0	18	0.01
KL26-01	81.9	84.8	0.0031		31	0.01	1.8	35	117	12	2	0.01	1	0.5	0.0	18	0.01
KL26-01	84.8	87.8	0.0032		32	0.02	2.6	217	1150	11	1	0.01	1	0.8	1.4	21	0.01
KL26-01	87.8	89.9	0.0019		19	0.02	2.3	27	225	10	1	1	1	0.5	0.0	19	0.01
KL26-01	89.9	92.9	0.0036		36	0.1	8.4	670	3800	20	4	2	1	3.3	3.3	21	0.01
KL26-01	92.9	95.9	0.003		30	0.01	4.1	370	2680	8	1	1	1	2.7	1.4	25	0.01
KL26-01	95.9	98.9	0.0027		27	0.01	5.3	176	2560	7	2	1	1	2.1	1.7	25	0.01
KL26-01	98.9	101.9	0.0027		27	0.01	2.3	262	670	7	1	1	1	1.6	0.6	26	0.01
KL26-01	101.9	104.9	0.0014		14	0.01	0.8	41	276	6	1	0.01	1	0.5	0.0	26	0.01
KL26-01	104.9	107.9	0.0009		9	0.01	0.1	36	192	2	3	0.01	1	0.8	0.6	27	0.01
KL26-01	107.9	110.9	0.0025		25	0.01	2.8	125	1850	4	4	0.01	1	2.5	1.2	29	0.01
KL26-01	110.9	113.9	0.0024		24	0.01	2.5	297	910	5	4	1	1	1.1	1.3	28	0.01
KL26-01	113.9	116.9	0.0025		25	0.01	3.8	171	1010	7	9	3	1	1.5	1.4	27	0.01
KL26-01	116.9	119.9	0.0019		19	0.01	2.2	310	870	5	14	1	1	0.8	0.0	16	0.01
KL26-01	119.9	122.9	0.002		20	0.01	3.8	750	2170	7	25	1	1	1.2	1.3	18	0.01
KL26-01	122.9	128.4	0.0016		16	0.01	3.3	399	950	23	8	0.01	1	1.1	0.9	13	0.01
KL26-01	128.4	131.2	0.001		10	0.01	1.3	132	208	6	1	0.01	1	0.5	0.7	13	0.01
KL26-01	131.2	134.9	0.0033		33	0.01	1.1	64	93	4	3	0.01	1	0.2	0.0	12	0.01
KL26-01	134.9	137.9	0.0017		17	0.02	2	140	218	7	3	0.01	1	0.9	0.0	14	0.01
KL26-01	137.9	140.9	0.0013		13	0.02	2.1	126	173	11	8	0.01	1	0.6	0.6	11	0.01
KL26-01	140.9	143.9	0.0019		19	0.01	3.4	82	147	10	9	0.01	1	1	1.2	16	0.01
KL26-01	143.9	146.9	0.0065		65	0.02	31	780	4800	8	8	0.01	1	6.6	5.5	16	0.01
KL26-01	146.9	149.9	0.0058		58	0.03	5.8	1010	1260	8	9	2	1	1.8	2.8	17	0.01
KL26-01	149.9	152.9	0.002		20	0.02	1.1	480	319	3	3	0.01	1	0.4	1.0	18	0.01
KL26-01	152.9	155.9	0.0015		15	0.01	1.2	109	158	6	3	1	1	0.6	1.4	17	0.01
KL26-01	155.9	159.3	0.0014		14	0.01	0.7	103	167	6	3	0.01	1	0.6	1.3	16	0.01
KL26-01	159.3	162.2	0.0015		15	0.02	3.3	81	107	5	1	0.01	1	0.7	1.6	14	0.01
KL26-01	162.2	164.5	0.002		20	0.01	0.7	101	92	8	8	0.01	1	0.7	1.9	17	0.01
KL26-01	164.5	167.2	0.0016		16	0.01	0.6	97	57	4	4	0.01	1	0.5	1.3	17	0.01
KL26-01	167.2	170.4	0.0028		28	0.01	0.1	125	75	5	5	0.01	1	0.2	0.9	15	0.01
KL26-01	170.4	172.9	0.0055		55	0.01	0.7	178	283	8	8	0.01	1	0.5	1.5	16	0.01
KL26-01	172.9	175.9	0.0024		24	0.24	2.9	1910	1800	10	8	0.01	1	2.7	2.5	15	0.01
KL26-01	175.9	178.9	0.0141		141	0.25	17.1	4000	2000	57	36	0.01	1	5	2.9	27	0.15
KL26-01	178.9	181.4	0.0249		249	0.18	26.7	27900	14800	25	57	34	1	10.7	7.5	14	0.31
KL26-01	181.4	184.4	0.0069		69	0.11	4	4700	3130	10	20	2	2	3.5	2.1	13	0.01
KL26-01	184.4	187.4	0.0057		57	0.36	3.8	1350	1750	55	23	8	1	3.8	2.7	13	0.01
KL26-01	187.4	190.4	0.0188		188	0.34	22.3	46400	32800	31	23	16	1	12.1	18.3	14	0.23
KL26-01	190.4	193.4	0.0103		103	0.14	4.5	4100	4650	30	24	3	2	2.7	3.1	19	0.01
KL26-01	193.4	196.4	0.049		490	0.2	15.8	16500	14800	180	63	4	1	14	15.8	21	0.42
KL26-01	196.4	199.4	0.075		750	0.39	37.4	24200	33800	240	127	30	1	27	62.5	19	0.4
KL26-01	199.4	202.2	0.0279		279	0.3	8.1	3880	5320	57	56	20	3	2.3	7.6	26	0.16
KL26-01	202.2	203.9	0.438		4380	0.96	52.6	91000	33700	420	113	160	30	13	128.0	91	0.17
KL26-01	203.9	206.9	0.087		870	1.24	1.6	1040	193	76	1250	164	6	4.1	4.2	82	0.28
KL26-01	206.9	209.9	0.094		940	0.75	1.6	750	232	350	728	18	5	24	7.0	148	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL26-01	209.9	212.9	0.107	1070	1.61	3	2900	374	290	2000	48	4	12.3	14.3	87	0.27
KL26-01	212.9	214.8	0.49	4900	1.03	4	5000	74	270	183	38	14	1.8	22.5	70	0.21
KL26-01	214.8	217.75	0.304	3040	1.19	2.9	95	34	200	1400	18	26	0.9	54.0	48	0.01
KL26-01	217.75	220.4	0.307	3070	1.22	2.1	115	36	410	970	14	9	0.6	12.3	49	0.01
KL26-01	220.4	223.4	0.345	3450	1.23	2.9	124	50	330	4800	70	12	0.4	13.9	57	0.16
KL26-01	223.4	226.4	0.404	4040	0.81	3.3	117	31	140	560	15	4	0.6	8.0	44	0.17
KL26-01	226.4	228.4	0.67	6700	1.03	5	132	40	90	650	7	5	1.1	8.0	48	0.25
KL26-01	228.4	230.9	1.22	12200	1	5.6	1160	119	2200	680	9	20	5.6	32.0	234	0.42
KL26-01	230.9	233.9	1.33	13300	1.64	9.2	3000	307	2600	1500	7	26	5	31.0	172	0.49
KL26-01	233.9	236.9	1.5	15000	2.24	9.4	550	80	650	828	10	16	0.6	10.8	133	0.15
KL26-01	236.9	239.9	0.06	600	1.02	1.1	228	123	81	3800	8	4	1	8.1	99	0.15
KL26-01	239.9	242.5	0.56	5600	1.88	4.3	2600	1930	110	425	7	12	1.3	22.0	126	0.11
KL26-01	242.5	243.9	1.87	18700	2.14	10.8	36400	315	110	28	11	75	0.8	66.5	136	0.18
KL26-01	243.9	247.4	2.08	20800	2.68	10.1	25800	105	370	2	37	35	1.9	59.8	132	0.51
KL26-01	247.4	250.4	1.33	13300	5.02	8.7	46900	120	350	1	122	21	2.2	68.0	154	0.4
KL26-01	250.4	252.9	0.88	8800	1.06	2.1	417	55	630	9	7	49	1.1	94.0	236	0.13
KL26-01	252.9	255.6	0.79	7900	1.4	3	344	50	480	510	0.01	36	4.7	9.5	125	0.34
KL26-01	255.6	257.9	0.87	8700	2.14	2.7	226	54	150	90	1	48	1.4	14.8	140	0.01
KL26-01	257.9	259.9	1.81	18100	2.42	6	1780	143	200	11	4	32	1.9	57.0	176	0.01
KL26-01	259.9	262.4	1.82	18200	2.44	7.1	264	24	190	34	1	35	0.9	25.5	96	0.01
KL26-01	262.4	265.4	2.73	27300	2.7	7.5	2010	381	1350	40	0.01	45	84	22.0	254	1.6
KL26-01	265.4	268.4	3.2	32000	1.86	5.4	760	298	1070	258	0.01	54	22	28.0	207	0.94
KL26-01	268.4	271.4	4.62	46200	2.26	3.9	1140	1090	310	130	0.01	59	68	42.5	228	0.37
KL26-01	271.4	273.7	7.1	71000	3.74	6	190	40	7	68	0.01	72	0.7	42.5	116	0.01
KL26-01	273.7	275.1	6.74	67400	4.65	7.5	140	22	1	156	0.01	53	0.5	38.0	201	0.01
KL26-01	275.1	278.9	1.98	19800	1.61	3.4	130	30	24	260	0.01	22	3.4	19.0	229	0.28
KL26-01	278.9	281.9	2.74	27400	1.12	6.4	2600	6200	110	223	3	30	12	14.0	224	0.74
KL26-01	281.9	284.9	0.68	6800	0.23	1.4	114	31	19	326	0.01	6	0.5	6.8	120	0.23
KL26-01	284.9	287.9	1	10000	0.21	1.7	219	52	17	201	0.01	12	0.4	7.0	102	0.44
KL26-01	287.9	290.9	1.63	16300	1.45	2.5	161	34	20	256	0.01	15	0.3	9.0	98	0.11
KL26-01	290.9	293.9	1.58	15800	1.88	1.8	740	60	180	70	0.01	29	4.1	15.0	93	0.1
KL26-01	293.9	296.9	1.67	16700	2.01	1.8	179	83	26	66	0.01	24	0.6	18.5	77	0.01
KL26-01	296.9	299.9	2.65	26500	2.55	3.3	141	50	300	23	0.01	33	0.6	18.0	142	0.01
KL26-01	299.9	302.9	1.47	14700	1.57	2.2	116	37	8	510	0.01	16	0.01	13.5	93	0.01
KL26-01	302.9	305.9	1.32	13200	0.7	2	640	126	13	232	0.01	17	0.5	10.0	100	0.17
KL26-01	305.9	308.9	2.37	23700	1.51	2.9	301	62	24	78	0.01	25	2.1	14.2	101	0.01
KL26-01	308.9	311.9	1.62	16200	1.32	2	48	26	0.01	163	0.01	29	0.01	16.5	111	0.1
KL26-01	311.9	314.9	1.31	13100	1.21	2.5	49	42	4	82	0.01	28	0.01	15.0	157	0.01
KL26-01	314.9	317.9	2.03	20300	1.05	2.1	53	66	8	84	0.01	21	0.2	15.0	181	0.01
KL26-01	317.9	320.9	1.73	17300	0.97	3.5	640	276	44	95	0.01	26	0.8	12.5	178	0.29
KL26-01	320.9	323.9	2.67	26700	1.57	3.4	580	252	220	690	0.01	33	1	21.5	123	0.24
KL26-01	323.9	325.8	2.24	22400	1.63	4.3	223	66	16	795	0.01	45	0.01	13.5	62	0.16
KL26-01	325.8	328.4	2.6	26000	1.5	2	160	15	0.01	650	0.01	23	0.01	8.3	56	0.01
KL26-01	328.4	331.4	3.25	32500	1.7	2.1	205	21	0.01	1400	0.01	56	0.01	13.3	39	0.01
KL26-01	331.4	334.4	1	10000	0.95	6.4	69	28	12	24	11	28	0.6	7.5	39	0.01
KL26-01	334.4	337.4	1.33	13300	1.23	1.5	196	31	3	603	0.01	43	0.4	10.5	78	0.01
KL26-01	337.4	340.4	3	30000	2.19	2.1	135	20	0.01	100	0.01	56	0.01	22.8	58	0.01
KL26-01	340.4	343.4	1.98	19800	1.12	2.7	97	13	0.01	703	0.01	58	0.2	10.5	39	0.01
KL26-01	343.4	346.4	2	20000	2.3	4	226	14	0.01	218	1	50	0.2	19.0	63	0.01
KL26-01	346.4	349.4	2.04	20400	3.01	7.8	340	18	3	27	4	39	0.2	23.0	38	0.01
KL26-01	349.4	350.9	1.29	12900	1.78	4	194	18	0.01	16	2	38	0.2	18.5	114	0.01
KL26-01	350.9	352.9	1.58	15800	1.74	5.2	240	19	0.01	13	0.01	24	0.3	14.5	73	0.01
KL26-01	352.9	355.4	1.48	14800	1.69	7.4	170	34	6	54	3	33	1	18.0	110	0.01
KL26-01	355.4	357.2	1.22	12200	1.44	7.1	62	23	5	76	4	31	0.3	12.5	106	0.01
KL26-01	357.2	359.9	0.98	9800	0.82	1.2	103	27	0.01	212	0.01	48	0.01	5.8	61	0.01
KL26-01	359.9	362.9	2.23	22300	1.22	11	101	30	37	382	149	47	1.3	20.0	170	0.01
KL26-01	362.9	365.9	2.98	29800	2.28	16.9	177	26	26	1270	82	91	0.6	30.0	178	0.01
KL26-01	365.9	367.4	1.51	15100	2.04	16.6	213	28	17	2900	9	31	0.4	19.5	79	0.01
KL26-01	367.4	369.7	1.4	14000	1.92	12.7	149	14	10	196	12	19	0.2	11.5	99	0.01
KL26-01	369.7	373.4	0.97	9700	0.81	5.8	225	18	10	26	8	8	0.2	9.5	68	0.01
KL26-01	373.4	376.4	0.31	3100	0.24	2.1	80	22	5	83	4	4	0.2	5.5	76	0.01
KL26-01	376.4	379.4	0.196	1960	0.24	1.2	60	28	14	95	4	3	0.01	6.5	83	0.01
KL26-01	379.4	382.4	0.62	6200	1.28	3.7	94	21	23	72	8	3	0.2	8.3	121	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL26-01	382.4	385.4	0.14	1400	0.26	1	69	27	8	935	6	2	0.9	4.0	73	0.01
KL26-01	385.4	389	0.0321	321	0.11	0.1	83	26	12	910	8	1	1.6	0.8	37	0.01
KL26-01	389	391.4	0.067	670	0.08	0.1	67	27	15	250	1	7	0.3	2.3	54	0.01
KL26-01	391.4	394.4	0.032	320	0.05	0.1	30	23	12	1100	2	3	0.9	1.3	69	0.01
KL26-01	394.4	397.4	0.0062	62	0.01	0.1	20	18	6	18	0.01	1	0.01	0.0	56	0.01
KL26-01	397.4	400.4	0.0273	273	0.04	0.1	24	18	18	54	0.01	3	0.01	0.7	58	0.01
KL26-01	400.4	403.4	0.53	5300	0.45	1.6	52	16	30	118	0.01	11	0.01	5.0	55	0.01
KL26-01	403.4	405.9	0.111	1110	0.13	0.6	234	41	26	36	0.01	21	0.01	9.8	40	0.01
KL26-01	405.9	407.8	3.18	31800	2.56	26.3	680	18	44	54	6	126	0.01	21.5	39	0.01
KL26-01	407.8	411.4	1.02	10200	0.82	6.7	180	40	160	46	7	82	0.3	11.0	33	0.01
KL26-01	411.4	414.2	0.52	5200	0.94	3.2	252	16	320	10	5	23	2	9.0	50	0.01
KL26-01	414.2	417.2	1.61	16100	3.12	7.3	4300	30	330	18	34	291	1.8	18.8	39	0.01
KL26-01	417.2	419.2	4.06	40600	4.77	23.7	53400	87	770	10	70	16	4.3	49.0	34	0.01
KL26-01	419.2	420.8	3.51	35100	2.21	15.7	21000	7100	400	4	70	5	5.7	52.5	40	0.01
KL26-01	420.8	422.8	0.095	950	0.35	2.5	1210	324	120	3	4	6	3.1	20.0	40	0.01
KL26-01	422.8	425.8	0.0206	206	0.07	0.9	730	530	26	3	2	1	0.7	4.8	26	0.01
KL26-01	425.8	427.8	0.0258	258	0.05	0.1	640	51	34	2	2	2	0.4	3.3	18	0.01
KL26-01	427.8	429.3	0.0185	185	0.15	0.7	450	170	25	6	2	3	0.4	3.3	20	0.01
KL26-01	429.3	430.5	1.2	12000	2.48	10.9	18100	1100	580	22	54	150	7	70.5	60	0.01
KL26-01	430.5	433	0.011	110	0.06	0.6	870	209	24	3	5	3	0.7	3.8	21	0.01
KL26-01	433	434.8	0.0062	62	0.03	0.1	74	46	12	12	1	4	0.3	3.1	20	0.01
KL26-01	434.8	437.8	0.156	1560	0.44	4.6	3400	500	210	108	26	16	4.8	18.5	113	0.01
KL26-01	437.8	440.8	0.093	930	0.17	5.2	4100	2500	92	17	2	6	5.4	11.6	45	0.01
KL26-01	440.8	442.7	0.069	690	0.47	3.5	10300	540	110	53	16	11	1.6	10.5	49	0.01
KL26-01	442.7	445.7	0.176	1760	3.68	4.2	28300	156	270	54	140	14	4.4	12.5	67	0.12
KL26-01	445.7	448	0.0297	297	2.57	0.7	320	62	250	568	18	1	3.8	4.3	50	0.17
KL26-01	448	449.8	0.0388	388	1.24	0.7	148	76	170	1040	38	1	2.7	6.5	67	0.01
KL26-01	449.8	451.5	0.0351	351	0.31	0.1	195	56	21	382	5	2	0.3	6.3	205	0.01
KL26-01	451.5	454.5	0.0225	225	0.06	0.1	84	26	20	80	0.01	4	0.7	0.0	54	0.01
KL26-01	454.5	457.2	0.0189	189	0.14	0.1	78	28	26	925	2	2	0.6	1.5	41	0.01
KL26-01	457.2	459.1	0.0126	126	0.08	0.1	129	45	32	3400	36	4	3	4.9	46	0.01
KL26-01	459.1	462	0.0197	197	0.21	0.6	133	46	74	3600	80	4	3.2	6.4	53	0.01
KL26-01	462	464.2	0.31	3100	2.38	15.2	1570	110	820	3160	190	7	10.1	8.5	40	0.01
KL26-01	464.2	467	0.0335	335	0.38	5	13400	3000	240	36	14	4	4.1	9.5	26	0.01
KL26-01	467	468.7	0.0217	217	0.24	2.6	9500	2100	110	19	5	2	3.2	5.3	18	0.01
KL26-01	468.7	470.8	0.0069	69	0.05	0.1	92	45	16	24	0.01	2	0.4	0.8	22	0.01
KL26-01	470.8	473.8	0.0021	21	0.07	0.1	64	26	9	4	0.01	3	0.2	0.8	16	0.01
KL26-01	473.8	476.8	0.0028	28	0.05	0.1	93	37	11	6	0.01	2	0.4	1.0	24	0.01
KL26-01	476.8	479.8	0.092	920	0.17	2	690	160	40	24	3	5	0.9	3.0	44	0.01
KL26-01	479.8	482.8	0.0061	61	0.15	0.1	84	32	11	8	1	5	0.3	0.0	20	0.01
KL26-01	482.8	484.8	0.004	40	0.06	0.1	67	80	13	7	0.01	4	0.4	0.8	23	0.01
KL26-01	484.8	487.8	0.0038	38	0.07	1.2	450	361	16	7	16	4	0.4	1.3	18	0.01
KL26-01	487.8	490.7	0.0105	105	0.03	0.1	338	212	9	9	2	3	0.3	1.3	14	0.01
KL26-01	490.7	493.7	0.0042	42	0.06	0.1	218	104	4	5	1	4	0.01	2.3	16	0.01
KL26-01	493.7	496.6	0.056	560	0.04	0.7	285	184	31	2	5	4	0.4	2.5	16	0.01
KL26-01	496.6	498.3	0.27	2700	0.09	34.5	16200	13200	340	7	150	3	2	18.0	34	0.01
KL26-02	0	3.1	0.0044	44	0.03	0.1	51	34	4	2	0.01	1	1.6	2.6	28	0.01
KL26-02	3.1	6.1	0.0101	101	0.02	2.2	430	182	14	7	3	1	2.2	3.8	27	0.01
KL26-02	6.1	9.1	0.0108	108	0.01	0.1	37	41	4	16	0.01	1	5.9	1.3	39	0.01
KL26-02	9.1	12.1	0.008	80	0.01	0.1	38	30	4	1	0.01	1	0.4	1.6	36	0.01
KL26-02	12.1	15.1	0.003	30	0.01	0.1	31	20	1	3	0.01	1	0.4	1.1	29	0.01
KL26-02	15.1	18.1	0.004	40	0.01	0.1	24	21	2	3	0.01	1	0.01	1.2	31	0.01
KL26-02	18.1	21.1	0.002	20	0.01	0.1	28	15	2	3	0.01	1	0.01	1.5	26	0.01
KL26-02	21.1	22.6	0.0015	15	0.01	0.1	51	23	3	1	0.01	1	0.01	1.6	24	0.01
KL26-02	22.6	26	0.0037	37	0.01	0.1	450	1160	5	6	0.01	3	1	3.7	26	0.01
KL26-02	26	28.6	0.0184	184	0.01	0.1	500	400	8	10	0.01	5	1.1	2.7	108	0.01
KL26-02	28.6	31.3	0.0504	504	0.01	3.4	3950	3320	21	16	0.01	7	2.9	19.2	134	0.01
KL26-02	31.3	33.1	0.086	860	0.16	57.6	26100	26800	45	20	46	1	23	109.0	72	0.01
KL26-02	33.1	34.7	0.0162	162	0.17	15.9	4710	6400	99	24	6	1	6.1	27.0	32	0.01
KL26-02	34.7	37.6	0.0091	91	0.75	61.6	470	11600	16	17	88	1	3.3	275.0	27	0.01
KL26-02	37.6	40.6	0.0301	301	0.16	7.6	295	6700	31	16	10	3	4.2	7.1	67	0.01
KL26-02	40.6	43.6	0.0333	333	0.1	21.3	2200	15500	11	18	23	1	5.9	68.0	36	0.01
KL26-02	43.6	47.1	0.0138	138	0.05	1.5	84	1540	13	25	0.01	1	2.5	1.2	34	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL26-02	47.1	49.6	0.0157		157	0.04	1.2	107	1410	7	14	0.01	1	2.9	0.6	46	0.01
KL26-02	49.6	51.5	0.0145		145	0.32	2.6	124	1990	24	16	0.01	1	2.6	1.9	37	0.01
KL26-02	51.5	54.1	0.0208		208	0.16	5.4	300	7400	36	17	1	1	7.5	3.0	38	0.01
KL26-02	54.1	57.1	0.0171		171	0.01	1.7	112	1240	14	7	0.01	1	3.6	0.7	23	0.01
KL26-02	57.1	60.1	0.015		150	0.04	2.4	98	520	14	4	2	1	3.5	0.0	20	0.01
KL26-02	60.1	63.1	0.0074		74	0.02	2.6	178	1740	12	11	2	1	3.5	0.5	21	0.01
KL26-02	63.1	66.1	0.0051		51	0.02	1.8	254	990	22	8	1	1	3.2	0.0	19	0.01
KL26-02	66.1	67.5	0.0057		57	0.01	1.1	146	440	23	14	0.01	1	2.5	0.0	24	0.01
KL26-02	67.5	70.6	0.0025		25	0.09	1.5	385	810	12	1	0.01	1	1.4	0.7	14	0.01
KL26-02	70.6	73.6	0.0097		97	0.03	4	1720	3420	10	6	0.01	1	2.6	1.4	34	0.01
KL26-02	73.6	76.6	0.0037		37	0.02	3	500	1340	2	2	1	1	1.2	1.0	25	0.01
KL26-02	76.6	79.6	0.0021		21	0.02	2.2	378	1560	0.01	3	0.01	1	1.2	1.0	18	0.01
KL26-02	79.6	82.6	0.0029		29	0.02	2.6	198	1140	8	4	0.01	1	2	0.9	22	0.01
KL26-02	82.6	85.6	0.0017		17	0.01	1.3	127	580	1	1	0.01	1	1.2	1.0	22	0.01
KL26-02	85.6	88.6	0.0038		38	0.01	2.4	530	1260	3	4	0.01	1	1.9	1.7	19	0.01
KL26-02	88.6	91.6	0.0014		14	0.01	1.8	107	960	0.01	1	0.01	1	1.3	0.9	24	0.01
KL26-02	91.6	96.1	0.0017		17	0.01	1.5	152	760	2	1	0.01	1	1.3	0.8	26	0.01
KL26-02	96.1	99.1	0.0228		228	0.02	1.1	64	389	3	4	0.01	1	0.8	1.3	28	0.01
KL26-02	99.1	102.1	0.0068		68	0.01	4.3	370	870	17	3	0.01	1	4.8	2.0	30	0.01
KL26-02	102.1	105.1	0.0124		124	0.01	1.1	157	265	1	3	0.01	1	0.5	0.0	22	0.01
KL26-02	105.1	108.1	0.0055		55	0.01	1.8	340	530	4	3	0.01	1	1.5	0.8	24	0.01
KL26-02	108.1	111.1	0.0057		57	0.01	4.5	380	660	9	3	0.01	2	2.4	1.2	26	0.01
KL26-02	111.1	117.1	0.0063		63	0.03	10	1130	1540	28	13	0.01	3	4.2	4.6	35	0.01
KL26-02	117.1	120.1	0.0066		66	0.01	3.4	408	890	6	15	0.01	1	2.9	0.9	34	0.01
KL26-02	120.1	124.3	0.0043		43	0.01	2.1	121	191	5	6	0.01	1	1.7	0.6	18	0.01
KL26-02	124.3	127.6	0.0034		34	0.01	2.6	116	250	7	13	0.01	1	1.4	1.4	14	0.01
KL26-02	127.6	130.6	0.0027		27	0.01	1.9	135	158	6	15	0.01	2	0.7	0.6	15	0.01
KL26-02	130.6	133.6	0.0246		246	0.09	13.5	345	430	220	9	2	4	6.1	10.1	26	0.01
KL26-02	133.6	136.6	0.0013		13	0.01	1.2	82	75	6	7	0.01	1	2.1	0.7	16	0.01
KL26-02	136.6	139.6	0.0016		16	0.01	1.5	204	253	3	3	0.01	1	0.4	0.8	13	0.01
KL26-02	139.6	142.6	0.0019		19	0.01	0.9	60	166	3	3	0.01	1	0.2	0.9	14	0.01
KL26-02	142.6	145.6	0.0012		12	0.01	0.7	150	152	5	5	0.01	1	0.01	0.7	12	0.01
KL26-02	145.6	148.6	0.0012		12	0.01	1	74	170	11	6	0.01	1	0.6	0.8	15	0.01
KL26-02	148.6	151.6	0.0037		37	0.01	1.5	188	187	7	3	0.01	1	0.5	1.3	15	0.01
KL26-02	151.6	153.6	0.0026		26	0.02	5.4	1180	1260	17	2	0.01	1	1.5	2.3	18	0.01
KL26-02	153.6	160.6	0.0023		23	0.01	1.5	214	530	19	3	0.01	1	1.3	2.8	20	0.01
KL26-02	160.6	163.6	0.0013		13	0.01	1	112	202	6	5	0.01	1	0.4	0.9	16	0.01
KL26-02	163.6	166.6	0.0013		13	0.01	1.1	242	139	9	4	0.01	1	0.3	1.3	18	0.01
KL26-02	166.6	169.6	0.0024		24	0.01	1.3	1040	365	8	5	0.01	1	0.7	2.8	17	0.01
KL26-02	169.6	172.6	0.0018		18	0.01	0.8	107	78	2	4	0.01	1	0.4	1.3	16	0.01
KL26-02	172.6	175.6	0.0026		26	0.01	0.6	241	175	7	4	0.01	1	0.8	1.7	17	0.01
KL26-02	175.6	178.6	0.0021		21	0.01	0.1	80	78	4	3	0.01	3	0.4	1.3	18	0.01
KL26-02	178.6	182.1	0.0165		165	0.01	0.6	187	385	4	11	0.01	2	0.5	1.2	12	0.01
KL26-02	182.1	184.6	0.0185		185	0.08	26.8	1280	6800	65	36	146	2	5.3	80.0	32	0.01
KL26-02	184.6	187.6	0.0076		76	0.04	1.3	620	470	8	8	0.01	1	1.3	2.5	14	0.01
KL26-02	187.6	191.4	0.0072		72	0.03	1.2	1320	1210	6	16	1	1	1.5	1.6	16	0.01
KL26-02	191.4	194.2	0.0071		71	0.04	0.6	870	810	5	10	0.01	1	0.6	1.5	14	0.01
KL26-02	194.2	198.1	0.0067		67	0.08	1.1	1050	1970	10	16	0.01	1	1.9	2.6	15	0.01
KL26-02	198.1	201.1	0.015		150	0.33	4.5	1640	1570	60	13	1	1	8.6	4.4	16	0.18
KL26-02	201.1	204.1	0.0047		47	0.04	0.9	710	780	10	14	1	1	1	1.4	12	0.01
KL26-02	204.1	207.1	0.008		80	0.03	1.6	1660	1590	16	29	1	1	2.2	3.4	12	0.01
KL26-02	207.1	210.1	0.0158		158	0.03	3.4	2440	2310	29	32	4	1	3.6	3.1	13	0.01
KL26-02	210.1	212.8	0.066		660	0.09	15.7	7800	14500	85	149	13	1	20.3	13.0	19	0.01
KL26-02	212.8	216	0.0236		236	0.07	14.6	1050	2740	47	154	42	2	2.6	27.0	16	0.01
KL26-02	216	217.7	0.0353		353	0.94	50	2010	6500	32	3240	1130	3	0.9	56.0	109	0.01
KL26-02	217.7	220.6	0.29		2900	0.37	7.8	11600	890	42	2780	55	10	1.5	5.2	130	0.01
KL26-02	220.6	223.6	0.0376		376	0.24	1.6	580	200	37	1430	4	4	0.9	3.3	77	0.25
KL26-02	223.6	226.6	0.0973		973	0.27	3.4	2630	422	38	860	80	3	0.8	7.8	54	0.01
KL26-02	226.6	228.6	0.146		1460	0.68	4.7	5100	185	42	1000	48	7	0.8	11.3	51	0.01
KL26-02	228.6	231.1	0.21		2100	1.21	3.9	10400	228	390	1200	74	13	5.2	22.6	95	0.3
KL26-02	231.1	234.1	0.43		4300	1.58	16.1	8300	328	1100	2580	117	43	27	16.2	99	0.18
KL26-02	234.1	237.1	0.28		2800	1.17	30.9	14500	6300	99	1860	118	41	3	71.0	77	0.01
KL26-02	237.1	238.6	0.49		4900	2.08	7.3	11900	350	56	263	79	16	3	70.0	56	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL26-02	238.6	240.9	0.26	2600	1.89	3.8	12600	54	220	1100	74	17	4.3	39.5	36	0.01
KL26-02	240.9	243.1	0.33	3300	1.3	4.8	22600	78	210	110	45	20	4.3	50.0	32	0.01
KL26-02	243.1	246.1	0.59	5900	1.24	5.4	28200	530	52	402	60	36	1.2	41.0	54	0.01
KL26-02	246.1	249.1	0.271	2710	0.69	2.2	261	52	95	3100	50	10	1.7	8.5	50	0.01
KL26-02	249.1	252.1	0.66	6600	1.2	8	1440	121	78	1290	6	35	0.5	15.8	64	0.01
KL26-02	252.1	255.1	2.37	23700	4.01	38.7	86000	20	36	820	119	165	1.4	44.8	56	0.1
KL26-02	255.1	258.1	0.84	8400	1.07	3.4	2400	125	28	105	3	57	1	13.5	25	0.1
KL26-02	258.1	261.1	0.77	7700	3.38	10.8	37200	6500	230	95	52	38	108	29.4	54	0.47
KL26-02	261.1	264.1	0.73	7300	5.36	3.5	1360	70	23	278	5	36	2	19.0	40	0.14
KL26-02	264.1	267.1	2.33	23300	4.61	24.2	1260	9900	360	138	90	30	18.5	83.3	136	0.01
KL26-02	267.1	270.1	1.32	13200	1.44	2.9	100	78	26	365	0.01	42	4.5	14.5	142	0.1
KL26-02	270.1	273.1	6.46	64600	3.72	17.3	180	84	180	1200	1	49	9.2	15.6	135	0.29
KL26-02	273.1	276.1	6.47	64700	10	31.4	316	149	960	280	1	50	48	14.4	191	1.06
KL26-02	276.1	279.1	7.65	76500	9.75	9.5	163	18	4	55	226	45	0.7	17.5	112	0.01
KL26-02	279.1	282.1	6.6	66000	6.41	15.8	720	287	1200	92	3	50	106	12.5	94	0.01
KL26-02	282.1	285.1	3.53	35300	5.51	3.5	142	43	11	108	1	37	2.4	25.0	206	0.01
KL26-02	285.1	286.5	3.97	39700	4.01	23.5	560	149	410	26	1	42	16.5	23.0	104	0.16
KL26-02	286.5	289.6	1.82	18200	0.78	2.6	271	67	38	204	1	17	0.01	7.0	62	0.01
KL26-02	289.6	292.6	2.06	20600	2.4	4.1	90	125	64	190	1	13	2.2	11.5	178	0.01
KL26-02	292.6	295.6	2.16	21600	2.33	5.2	1140	440	850	56	2	14	50	21.0	275	0.24
KL26-02	295.6	298.6	1.77	17700	1.49	4.3	210	80	65	95	1	11	1.4	10.0	173	0.18
KL26-02	298.6	301.6	2.24	22400	2.24	3.8	120	32	5	80	1	14	0.5	16.0	117	0.01
KL26-02	301.6	304.6	2.17	21700	1.4	3.6	104	34	48	134	1	21	0.01	15.0	162	0.01
KL26-02	304.6	307.6	1.22	12200	0.63	2	147	75	8	126	0.01	10	0.6	13.0	112	0.01
KL26-02	307.6	310.6	1.87	18700	1.03	2.8	248	77	9	108	1	8	0.3	9.5	72	0.01
KL26-02	310.6	313.6	2.11	21100	1.77	3.2	55	12	0.01	57	0.01	15	0.3	10.0	91	0.01
KL26-02	313.6	316.6	2.26	22600	3.11	3.5	44	14	0.01	107	1	12	0.01	19.0	75	0.01
KL26-02	316.6	319.6	1.69	16900	1.27	2.7	42	16	0.01	79	1	11	0.01	9.0	61	0.01
KL26-02	319.6	322.6	1.94	19400	1.89	3.2	56	16	2	34	1	14	0.4	9.0	57	0.01
KL26-02	322.6	325.6	2.43	24300	1.18	4.6	57	17	3	86	1	14	0.4	12.0	51	0.01
KL26-02	325.6	328.6	2.25	22500	0.59	3	53	19	2	81	1	15	0.6	16.5	81	0.01
KL26-02	328.6	331.6	2.36	23600	1.17	3.9	30	10	1	155	0.01	13	0.3	15.0	92	0.01
KL26-02	331.6	334.6	2.09	20900	1.45	3.2	32	8	0.01	132	1	9	0.01	8.0	130	0.01
KL26-02	334.6	337.6	1.87	18700	1.25	3.2	42	10	4	113	1	10	0.4	7.5	110	0.01
KL26-02	337.6	340.6	1.57	15700	0.89	2.4	36	10	0.01	91	0.01	13	0.01	12.0	218	0.01
KL26-02	340.6	343.6	2.03	20300	0.96	3.5	212	117	300	229	1	14	3.4	6.5	69	0.01
KL26-02	343.6	346.6	2.61	26100	1.11	1.5	40	12	1	70	1	13	0.2	17.5	85	0.01
KL26-02	346.6	349.6	2.32	23200	1.39	3.2	56	17	1	860	1	16	0.2	22.0	95	0.01
KL26-02	349.6	352.6	1.8	18000	0.83	2.8	32	16	0.01	680	1	15	0.01	10.5	56	0.01
KL26-02	352.6	355.6	1.78	17800	1.21	3.3	66	34	4	133	1	12	0.6	8.0	54	0.01
KL26-02	355.6	358.6	1.35	13500	0.91	1.6	19	9	0.01	57	1	11	0.2	11.0	41	0.01
KL26-02	358.6	363	1.09	10900	0.72	1.7	36	13	1	50	1	12	0.01	7.0	34	0.01
KL26-02	363	366	1.51	15100	0.84	2.3	38	13	0.01	185	2	15	0.01	8.5	56	0.01
KL26-02	366	367.7	2.49	24900	1.84	4.1	34	14	1	40	6	11	0.01	16.5	71	0.01
KL26-02	367.7	372	1.76	17600	1.29	3.7	219	87	34	120	1	13	3.3	8.5	71	0.01
KL26-02	372	375	0.99	9900	0.96	6.2	4200	3300	97	470	1	13	15.1	10.0	39	0.01
KL26-02	375	378	1.77	17700	1.59	34.8	32000	16300	1750	680	2	14	110	12.7	34	0.95
KL26-02	378	381	1.61	16100	1.43	34.5	28300	14900	1800	660	1	16	130	12.5	70	1.38
KL26-02	381	384	1.65	16500	1.35	10.5	3900	2200	210	144	1	21	13.6	13.5	79	0.1
KL26-02	384	387	1.61	16100	1.27	4.8	356	172	170	146	0.01	42	3	9.3	61	0.01
KL26-02	387	390	1.62	16200	1.35	2.8	351	151	35	27	1	23	1.8	8.0	98	0.01
KL26-02	390	393	2.2	22000	1.71	6	560	340	810	24	1	22	11.3	11.0	84	0.01
KL26-02	393	396	2.29	22900	1.35	2.8	660	287	270	24	1	28	3	20.0	74	0.01
KL26-02	396	398.4	2.58	25800	3.13	3.7	1180	530	83	22	6	25	6.5	20.0	64	0.01
KL26-02	398.4	402	1.2	12000	0.51	3.7	2120	336	370	120	1	6	18.8	11.5	36	0.25
KL26-02	402	405	1.06	10600	0.38	23.1	5000	2500	1500	67	5	7	255	8.0	24	1.32
KL26-02	405	408	0.59	5900	0.23	6.1	626	168	610	68	0.01	8	41	6.0	27	0.12
KL26-02	408	411	0.7	7000	0.23	3.7	303	354	230	83	0.01	6	18	7.0	41	0.01
KL26-02	411	414	1.07	10700	0.31	4.2	285	182	340	84	0.01	10	13	11.3	53	0.01
KL26-02	414	417	0.66	6600	0.52	1.4	112	68	17	114	0.01	12	0.9	7.2	61	0.01
KL26-02	417	420	0.99	9900	0.56	1.8	167	122	12	143	0.01	10	0.5	9.0	50	0.01
KL26-02	420	423	1.65	16500	0.28	12.4	1870	3900	380	400	1	13	61	11.0	53	0.3
KL26-02	423	426	0.9	9000	0.33	19.4	17300	16300	1200	102	3	7	160	10.5	64	2.68

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL26-02	426	429	1.01	10100	0.31	1.9	1390	290	47	203	1	9	2.4	9.3	61	0.01
KL26-02	429	432	1.3	13000	0.45	2.3	600	720	14	219	0.01	13	2.8	7.3	76	0.01
KL26-02	432	435	1.16	11600	0.39	2	1000	650	150	230	0.01	12	2.1	9.3	90	0.01
KL26-02	435	437.5	1.31	13100	0.58	2	300	280	110	275	0.01	15	1.7	8.8	70	0.1
KL26-02	437.5	441	1.24	12400	0.69	2.4	2040	960	410	197	0.01	15	14	9.0	86	0.12
KL26-02	441	444	1.09	10900	0.55	2.4	368	450	130	207	0.01	11	7.4	9.0	60	0.01
KL26-02	444	447	0.61	6100	0.25	1.8	245	81	10	206	0.01	10	0.8	7.8	92	0.01
KL26-02	447	450	0.78	7800	0.33	2.5	1150	1030	120	317	0.01	13	9.8	7.8	100	0.01
KL26-02	450	453	1.46	14600	0.64	2.2	76	14	2	412	0.01	20	0.3	9.8	106	0.01
KL26-02	453	455.5	0.92	9200	0.36	1.2	110	14	3	300	0.01	16	0.3	8.5	354	0.01
KL26-02	455.5	459	0.69	6900	0.48	1.1	125	34	19	210	0.01	12	0.6	7.5	231	0.01
KL26-02	459	462	1.2	12000	0.5	1.4	282	112	76	470	0.01	15	1.8	8.0	304	0.01
KL26-02	462	465	1.37	13700	0.72	1.5	66	12	19	241	0.01	18	0.3	10.0	281	0.01
KL26-02	465	466.3	1.61	16100	0.84	2.3	192	25	5	315	0.01	20	0.3	13.0	340	0.01
KL26-02	466.3	468	3.1	31000	1.5	4	215	37	20	640	0.01	48	0.4	18.0	236	0.01
KL26-02	468	470	2.01	20100	1.37	4.6	249	80	380	440	0.01	15	17.9	13.0	251	0.01
KL26-02	470	471.5	2.62	26200	1.27	3.3	93	16	33	260	0.01	29	1.9	14.0	305	0.01
KL26-02	471.5	474.2	3.54	35400	2.08	4.5	112	15	9	93	0.01	40	0.5	21.0	214	0.01
KL26-02	474.2	477	1.3	13000	0.71	2.1	73	26	4	254	0.01	17	0.5	10.0	273	0.01
KL26-02	477	480.6	1.27	12700	0.75	2	105	40	3	300	0.01	19	0.4	10.3	301	0.01
KL26-02	480.6	482.8	2.02	20200	1.29	3.6	151	26	6	273	0.01	34	0.01	16.5	207	0.01
KL26-02	482.8	486	1.46	14600	0.74	2.9	293	63	9	307	0.01	24	0.6	14.5	254	0.01
KL26-02	486	488.5	1.21	12100	0.63	2	261	81	15	388	0.01	17	0.6	11.0	264	0.01
KL26-02	488.5	491.5	1.39	13900	0.67	2.1	102	17	6	287	0.01	18	0.2	10.0	290	0.01
KL26-02	491.5	494.6	1.24	12400	0.57	2.2	72	9	2	300	0.01	18	0.01	8.5	316	0.01
KL26-02	494.6	496.8	1.14	11400	0.49	2.1	106	20	2	287	0.01	17	0.01	8.5	357	0.01
KL26-02	496.8	499.3	3.61	36100	2.13	5.5	156	25	3	83	0.01	33	0.01	14.0	170	0.01
KL26-02	499.3	500.8	2.81	28100	1.37	4.6	200	95	2	102	0.01	25	0.3	10.0	134	0.01
KL26-02	500.8	503.9	1.84	18400	0.71	4.1	93	10	0.01	367	0.01	28	0.01	9.5	100	0.01
KL26-02	503.9	506.3	2.01	20100	1	2.5	71	8	0.01	347	0.01	42	0.01	8.2	60	0.01
KL26-02	506.3	508.5	0.28	2800	0.21	0.7	73	14	2	54	0.01	16	0.01	5.1	38	0.01
KL26-02	508.5	510	0.9	9000	0.6	1.5	73	9	0.01	590	0.01	36	0.01	11.1	32	0.01
KL26-02	510	513	1.27	12700	1.02	2.7	142	7	3	150	0.01	17	0.6	5.9	61	0.01
KL26-02	513	516	1.89	18900	1.22	4.1	69	6	0.01	116	1	17	0.3	12.0	46	0.01
KL26-02	516	519	0.93	9300	0.93	2.4	250	11	3	7	4	19	0.5	7.0	35	0.01
KL26-02	519	522	1.14	11400	0.66	3	76	8	0.01	5	0.01	20	0.01	6.0	24	0.01
KL26-02	522	523.9	0.429	4290	0.35	1.1	156	10	10	10	0.01	17	1	4.4	27	0.01
KL26-02	523.9	525.7	0.96	9600	0.41	2.5	116	11	4	28	0.01	32	0.01	22.5	66	0.01
KL26-02	525.7	529.1	1.38	13800	2.31	11.6	560	11	10	40	32	54	0.01	29.3	31	0.01
KL26-02	529.1	531	0.67	6700	1.12	4.1	197	14	10	21	3	32	8.2	10.3	31	0.01
KL26-02	531	534	2.21	22100	1.75	5.3	178	9	6	37	8	48	6.1	39.0	31	0.01
KL26-02	534	536.5	2.5	25000	1.71	8.4	194	8	28	38	3	89	0.01	39.5	35	0.01
KL26-02	536.5	539.5	1.74	17400	1.48	5.1	283	9	7	29	1	70	0.6	13.0	38	0.01
KL26-02	539.5	542.7	0.72	7200	0.6	2.2	210	8	5	19	1	43	0.01	8.9	37	0.01
KL26-02	542.7	545.8	1.2	12000	0.86	4	201	14	26	118	1	37	0.01	14.3	15	0.01
KL26-02	545.8	549.1	1.39	13900	0.72	3.7	147	6	20	321	1	32	0.01	13.2	11	0.01
KL26-02	549.1	552	2	20000	1.18	6.6	224	6	6	122	1	36	0.01	11.6	12	0.01
KL26-02	552	555	2.16	21600	1.84	7.8	211	6	5	139	6	40	0.01	20.5	17	0.01
KL26-02	555	558	0.75	7500	0.49	3.6	101	10	9	120	11	27	0.01	63.5	60	0.01
KL26-02	558	561	0.86	8600	2.11	5	440	7	2	16	4	32	1.6	17.0	34	0.01
KL26-02	561	564	1.05	10500	0.77	6	940	7	12	11	3	40	0.01	21.0	34	0.01
KL26-02	564	567	0.76	7600	0.53	5	1310	16	11	7	5	25	0.6	26.1	36	0.01
KL26-02	567	570	0.61	6100	0.49	6.1	690	47	27	37	44	16	0.01	14.0	17	0.01
KL26-02	570	573	0.443	4430	0.47	3.8	524	29	17	23	6	6	0.01	8.0	18	0.01
KL26-02	573	576	0.52	5200	0.38	3.2	398	12	9	37	28	11	0.2	13.1	34	0.01
KL26-02	576	579	0.52	5200	0.45	3.4	510	13	11	22	4	10	0.4	9.5	23	0.01
KL26-02	579	582	0.54	5400	0.44	2.8	416	12	18	6	2	7	0.4	7.5	26	0.01
KL26-02	582	585	0.159	1590	0.1	1	216	9	6	3	1	3	0.2	4.3	17	0.01
KL26-02	585	588	0.095	950	0.08	0.9	206	11	5	4	1	3	0.01	2.6	16	0.01
KL26-02	588	589.9	0.488	4880	0.24	2.9	532	11	13	6	3	19	0.4	20.3	27	0.01
KL26-02	589.9	592.1	0.77	7700	0.33	3.1	330	13	21	25	2	42	0.01	21.0	34	0.01
KL26-02	592.1	594	1.6	16000	0.76	3.4	338	12	1	87	0.01	62	0.4	9.8	26	0.01
KL26-02	594	597	1.4	14000	0.72	3.4	189	12	1	14	0.01	44	0.01	20.2	23	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL26-02	597	600	3.59	35900	1.75	5.9	330	13	0.01	10	0.01	59	0.01	21.5	18	0.01
KL26-02	600	603	2.03	20300	1.01	3.6	221	11	0.01	4	0.01	43	0.01	16.0	24	0.01
KL26-02	603	606	1.74	17400	0.84	2.2	160	10	1	15	0.01	41	0.01	17.0	26	0.01
KL26-02	606	609	1.17	11700	0.62	2.1	122	9	3	8	0.01	36	0.01	10.5	20	0.01
KL26-02	609	612	2.1	21000	0.81	4.1	110	10	2	59	0.01	29	0.3	16.0	27	0.01
KL26-02	612	614.7	0.74	7400	0.47	2.2	95	9	5	37	0.01	13	0.4	9.3	33	0.01
KL26-02	614.7	618	0.31	3100	0.16	0.8	43	9	2	84	0.01	9	0.01	7.0	20	0.01
KL26-02	618	621	0.325	3250	0.21	1	45	10	2	48	0.01	6	0.01	5.3	20	0.01
KL26-02	621	624	0.2	2000	0.06	0.5	39	10	0.01	40	0.01	4	0.01	2.0	16	0.01
KL26-02	624	627	0.277	2770	0.08	0.7	47	13	0.01	41	0.01	15	0.5	9.5	18	0.01
KL26-02	627	630	0.469	4690	0.29	1.1	76	18	3	23	0.01	12	1.1	5.5	21	0.01
KL26-02	630	633	0.334	3340	0.15	0.7	66	10	1	26	0.01	12	0.01	4.0	43	0.01
KL26-02	633	636	0.237	2370	0.13	0.6	70	10	0.01	30	0.01	11	0.01	3.3	41	0.01
KL26-02	636	639	0.174	1740	0.09	0.5	65	13	1	121	0.01	12	0.01	4.1	41	0.01
KL26-02	639	642	0.278	2780	0.15	0.7	67	13	1	52	0.01	12	0.01	2.8	51	0.01
KL26-02	642	645	0.394	3940	0.36	1.1	71	10	2	11	0.01	9	0.3	4.8	53	0.01
KL26-02	645	648	0.62	6200	0.34	1.6	82	14	1	8	0.01	14	0.01	7.9	50	0.01
KL26-02	648	651	0.52	5200	0.24	1	96	20	16	610	0.01	11	0.6	5.8	32	0.01
KL26-02	651	653.5	0.72	7200	0.41	2	111	19	4	196	0.01	14	0.4	9.0	95	0.01
KL26-02	653.5	657	0.338	3380	0.18	0.9	334	42	62	123	0.01	9	2	7.6	116	0.01
KL26-02	657	660	0.458	4580	0.23	2.2	269	35	44	21	0.01	10	1.8	17.0	33	0.01
KL26-02	660	663	0.56	5600	0.21	1.4	123	25	6	68	0.01	8	0.6	7.6	35	0.01
KL26-02	663	666	0.21	2100	0.07	0.1	20	11	2	167	0.01	10	0.3	7.5	16	0.01
KL26-02	666	669	0.313	3130	0.23	0.9	36	9	1	43	0.01	5	0.2	4.5	17	0.01
KL26-02	669	672	0.242	2420	0.1	0.1	31	12	1	41	0.01	6	0.2	4.0	24	0.01
KL26-02	672	675	0.228	2280	0.1	1.9	504	410	97	22	2	4	12	5.1	38	0.01
KL26-02	675	678	0.303	3030	0.13	0.1	36	11	4	228	0.01	5	0.01	4.3	20	0.01
KL26-02	678	683.3	0.17	1700	0.05	0.1	18	8	0.01	61	0.01	3	0.3	2.0	24	0.01
KL26-02	683.3	686.4	0.24	2400	0.15	0.8	17	7	0.01	156	0.01	4	0.3	3.3	15	0.01
KL26-02	686.4	690	0.09	900	0.04	0.1	10	1	0.01	74	0.01	3	0.3	2.5	10	0.01
KL26-02	690	693	0.6	6000	0.17	1.2	46	10	1	1060	0.01	6	0.2	5.3	5	0.01
KL26-02	693	696	0.279	2790	0.14	0.6	65	14	12	35	0.01	12	0.01	5.5	8	0.01
KL26-02	696	699	0.391	3910	0.18	0.7	53	9	3	39	0.01	7	0.01	5.0	12	0.01
KL26-02	699	702	1.42	14200	0.56	3.2	510	113	240	134	0.01	19	4.7	13.9	28	0.01
KL26-02	702	705	1.36	13600	0.65	2.8	138	19	6	88	0.01	10	0.01	10.9	30	0.01
KL26-02	705	708.8	0.59	5900	0.3	2.2	140	11	11	19	0.01	37	8	7.3	25	0.01
KL26-02	708.8	710.5	0.17	1700	0.07	0.9	151	12	0.01	1	0.01	9	0.01	1.6	23	0.01
KL26-02	710.5	713.2	0.98	9800	0.37	6.9	570	18	4	4	0.01	16	0.01	11.0	27	0.01
KL26-02	713.2	716.9	0.464	4640	0.16	3	308	12	4	4	0.01	13	0.3	11.3	31	0.01
KL26-02	716.9	719.3	0.73	7300	0.85	2.7	161	11	8	8	3	24	0.3	15.7	50	0.01
KL26-02	719.3	722.4	1.07	10700	1.2	3.3	224	256	3	58	4	30	0.01	11.5	54	0.01
KL26-02	722.4	725.5	0.62	6200	0.24	1.5	87	26	2	76	0.01	27	0.01	7.4	28	0.01
KL26-02	725.5	728.6	0.382	3820	0.12	0.8	86	15	0.01	28	0.01	26	0.01	6.5	40	0.01
KL26-02	728.6	732	0.303	3030	0.09	0.1	80	15	1	41	0.01	23	0.01	2.8	37	0.01
KL26-02	732	735	0.81	8100	0.33	1.5	145	15	0.01	24	0.01	20	0.01	6.5	34	0.01
KL26-02	735	738	1.19	11900	0.63	3.2	245	13	1	23	0.01	28	1.2	11.9	40	0.01
KL26-02	738	741	2.12	21200	1.04	4.7	500	13	4	43	0.01	34	0.6	13.0	31	0.01
KL26-02	741	744	1.42	14200	0.73	3	185	17	6	86	0.01	33	0.3	11.0	26	0.01
KL26-02	744	747	1.05	10500	0.6	2.9	176	15	4	13	3	42	0.9	9.3	27	0.01
KL26-02	747	750	1.53	15300	0.69	3.2	162	8	4	16	2	46	0.6	9.2	29	0.01
KL26-02	750	753	1.13	11300	0.54	3	117	12	7	56	0.01	34	0.2	12.4	26	0.01
KL26-02	753	756	0.7	7000	0.39	1.5	125	12	4	27	0.01	25	0.5	8.8	31	0.01
KL26-02	756	759	0.99	9900	0.43	2.2	155	10	9	15	0.01	33	0.01	24.0	24	0.01
KL26-02	759	762	0.73	7300	0.29	1.7	101	10	1	112	0.01	25	0.9	9.7	31	0.01
KL26-02	762	765	0.501	5010	0.19	1	208	13	5	24	0.01	20	0.01	12.5	27	0.01
KL26-02	765	768	1.33	13300	0.41	2.4	178	9	1	34	0.01	26	0.01	10.4	34	0.01
KL26-02	768	771	0.73	7300	0.28	1.2	440	12	0.01	11	0.01	26	0.01	7.0	26	0.01
KL26-02	771	774	0.55	5500	0.19	1.3	95	11	0.01	17	0.01	17	0.01	7.2	24	0.01
KL26-02	774	776.5	0.56	5600	0.21	1.2	98	11	0.01	7	0.01	20	0.01	6.5	25	0.01
KL26-02	776.5	779.5	0.67	6700	0.25	1.3	173	9	3	60	0.01	20	2	7.0	95	0.01
KL26-02	779.5	782.7	1.23	12300	0.48	2.2	230	12	4	41	0.01	28	2.9	17.5	28	0.01
KL26-02	782.7	785.9	0.71	7100	0.27	1.9	297	10	3	13	0.01	23	1.1	9.4	63	0.01
KL26-02	785.9	789	0.84	8400	0.29	2.5	374	205	5	20	0.01	20	0.3	9.3	26	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL26-02	789	792	0.82	8200	0.3	1.8	204	41	4	25	0.01	21	0.5	9.4	41	0.01
KL26-02	792	795	0.57	5700	0.26	1.5	164	10	4	6	0.01	22	0.5	5.8	31	0.01
KL26-02	795	798	0.65	6500	0.25	1.2	71	9	3	11	0.01	18	0.01	6.0	23	0.01
KL26-02	798	801	0.76	7600	0.25	1.2	64	9	3	50	0.01	19	0.01	8.2	27	0.01
KL26-02	801	803.7	1.02	10200	0.27	1.4	81	8	5	180	0.01	21	0.01	9.6	25	0.01
KL26-02	803.7	806	1	10000	0.33	1.7	111	9	3	8	0.01	24	0.01	6.6	26	0.01
KL26-02	806	808.8	0.489	4890	0.14	0.8	132	9	2	18	0.01	22	0.01	6.6	26	0.01
KL26-02	808.8	810.4	0.193	1930	0.05	0.5	26	5	0.01	239	0.01	15	0.01	8.2	16	0.01
KL26-02	810.4	812.5	0.503	5030	0.17	1	229	24	10	15	0.01	22	0.01	7.2	31	0.01
KL26-02	812.5	815.5	0.21	2100	0.06	0.5	41	6	0.01	23	0.01	16	0.01	4.3	30	0.01
KL26-02	815.5	818.5	0.448	4480	0.09	0.6	43	6	1	123	0.01	25	0.01	8.3	24	0.01
KL26-02	818.5	821.5	0.106	1060	0.03	0.1	33	7	6	9	0.01	10	0.01	2.8	17	0.01
KL26-02	821.5	825	0.496	4960	0.14	1.2	56	6	3	23	0.01	17	0.01	6.4	26	0.01
KL26-02	825	828	0.087	870	0.01	0.1	18	5	0.01	9	0.01	7	0.01	1.3	14	0.01
KL26-02	828	831	0.496	4960	0.11	1.2	44	1	0.01	39	0.01	19	0.01	8.8	20	0.01
KL26-02	831	834	0.118	1180	0.02	0.1	24	5	2	5	0.01	11	0.01	2.5	14	0.01
KL26-02	834	837	0.178	1780	0.05	0.1	42	6	1	4	0.01	18	0.01	3.4	13	0.01
KL26-02	837	840	0.91	9100	0.14	1.4	61	5	1	53	0.01	18	0.01	10.4	15	0.01
KL26-02	840	843	0.346	3460	0.06	0.6	64	5	3	40	0.01	18	0.01	5.1	16	0.01
KL26-02	843	846	0.37	3700	0.07	0.7	46	6	2	16	0.01	20	0.01	4.3	18	0.01
KL26-02	846	849	0.14	1400	0.02	0.1	42	5	1	4	0.01	15	0.01	3.1	22	0.01
KL26-02	849	852	0.15	1500	0.17	1.5	67	8	3	44	0.01	21	0.01	7.2	25	0.01
KL26-02	852	855	1.23	12300	0.31	2.5	118	7	2	124	0.01	37	0.01	9.4	26	0.01
KL26-02	855	858	0.287	2870	0.06	0.5	54	8	3	47	0.01	20	0.01	5.2	25	0.01
KL26-02	858	861	0.248	2480	0.06	0.5	52	8	0.01	9	0.01	22	0.01	4.2	30	0.01
KL26-02	861	864	0.398	3980	0.13	0.7	57	7	2	20	0.01	23	0.01	4.4	36	0.01
KL26-02	864	867	0.385	3850	0.18	0.7	77	9	0.01	11	0.01	16	0.01	4.0	26	0.01
KL26-02	867	870	0.473	4730	0.33	0.8	75	8	0.01	12	0.01	19	0.01	4.1	24	0.01
KL26-02	870	873	0.506	5060	0.21	1.9	126	27	8	42	0.01	32	3.2	9.4	22	0.01
KL26-02	873	875	1.67	16700	0.41	2.6	103	8	1	192	0.01	28	0.01	13.2	26	0.01
KL26-02	875	876.6	0.47	4700	0.13	0.9	43	7	1	25	0.01	13	0.01	3.1	16	0.01
KL26-02	876.6	879.3	0.274	2740	0.09	0.7	37	6	1	15	0.01	7	0.2	3.4	12	0.01
KL26-02	879.3	882	0.107	1070	0.01	0.1	35	9	1	84	0.01	5	0.01	2.0	32	0.01
KL26-02	882	885	0.2	2000	0.1	0.1	39	8	1	11	0.01	3	0.01	1.5	12	0.01
KL26-02	885	888	0.111	1110	0.03	0.1	18	5	0.01	24	0.01	7	0.01	2.9	12	0.01
KL26-02	888	891.1	0.7	7000	0.41	1.6	106	7	2	102	0.01	21	0.01	7.4	27	0.01
KL26-02	891.1	895.2	0.38	3800	0.12	1	46	6	1	71	0.01	13	0.01	3.3	25	0.01
KL26-02	895.2	897.3	0.53	5300	0.24	1.4	78	9	3	17	0.01	24	0.2	5.6	23	0.01
KL26-02	897.3	900	0.486	4860	0.09	1	36	1	4	288	0.01	13	0.01	6.8	19	0.01
KL26-02	900	903	0.345	3450	0.11	1	68	6	3	20	0.01	15	0.01	4.5	23	0.01
KL26-02	903	906	0.4	4000	0.17	1.1	46	5	3	31	0.01	19	0.01	6.3	23	0.01
KL26-02	906	909	0.23	2300	0.04	0.9	38	5	1	320	0.01	10	0.01	3.3	53	0.01
KL26-02	909	912.8	0.06	600	0.05	0.1	10	1	1	25	0.01	2	0.01	1.2	14	0.01
KL26-02	912.8	915	0.37	3700	0.2	1.1	48	6	4	25	0.01	12	0.01	4.3	23	0.01
KL26-02	915	918	0.288	2880	0.13	1	36	5	2	26	0.01	8	0.01	4.9	22	0.01
KL26-02	918	921	0.067	670	0.03	0.1	16	1	0.01	34	0.01	3	0.01	2.0	11	0.01
KL26-02	921	924	0.131	1310	0.06	0.6	26	8	2	47	0.01	4	0.01	3.1	6	0.01
KL26-02	924	927	0.122	1220	0.03	0.5	27	6	3	18	0.01	9	0.01	3.0	13	0.01
KL26-02	927	930	0.109	1090	0.06	0.5	24	5	2	8	0.01	6	0.01	1.8	13	0.01
KL26-02	930	933	0.068	680	0.01	0.5	8	1	1	6	0.01	3	0.01	1.5	7	0.01
KL26-02	933	936	0.05	500	0.01	0.1	8	5	1	30	0.01	3	0.01	1.3	12	0.01
KL26-02	936	939	0.0115	115	0.01	0.1	3	5	1	95	0.01	3	0.01	0.0	9	0.01
KL26-02	939	942	0.068	680	0.02	0.1	24	6	2	9	0.01	2	0.01	1.4	13	0.01
KL26-02	942	945	0.058	580	0.02	0.1	26	5	2	10	0.01	4	0.01	0.9	16	0.01
KL26-02	945	948	0.21	2100	0.14	0.8	38	8	3	31	0.01	5	0.01	2.4	14	0.01
KL26-02	948	951	0.0324	324	0.01	0.1	9	5	1	15	0.01	2	0.01	0.0	11	0.01
KL26-02	951	954	0.161	1610	0.14	1	56	49	3	10	1	6	0.01	3.8	17	0.01
KL26-02	954	957	0.466	4660	0.36	1.3	58	8	2	3	0.01	11	0.01	4.0	14	0.01
KL26-02	957	959.3	0.31	3100	0.26	1	52	8	3	6	0.01	10	0.01	3.8	19	0.01
KL26-02	959.3	960.9	0.65	6500	0.27	1.6	120	9	2	2	0.01	30	0.01	6.0	25	0.01
KL26-02	960.9	963	0.196	1960	0.08	0.7	46	7	3	11	0.01	11	0.01	2.3	23	0.01
KL26-02	963	967.1	0.185	1850	0.06	0.9	34	6	1	12	0.01	12	0.01	3.2	28	0.01
KL26-02	967.1	969.9	0.0055	55	0.03	0.8	39	24	12	2	0.01	4	1.1	2.7	24	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL26-02	969.9	973.6	0.16	1600	0.1	0.8	1820	22	4	23	1	30	0.01	5.1	21	0.01
KL26-02	973.6	978	0.81	8100	0.25	1.8	82	6	3	24	0.01	26	0.01	7.2	18	0.01
KL26-02	978	981	0.26	2600	0.07	0.9	52	7	2	33	0.01	21	0.01	3.3	15	0.01
KL26-02	981	983.8	0.061	610	0.03	0.6	43	6	3	104	7	14	0.01	1.9	13	0.01
KL26-02	983.8	987	0.187	1870	0.07	0.7	69	9	1	113	0.01	24	0.01	2.9	17	0.01
KL26-02	987	990	0.111	1110	0.05	0.6	26	8	3	14	0.01	4	0.01	1.7	15	0.01
KL26-02	990	993	0.042	420	0.01	0.5	12	5	2	35	0.01	5	0.01	0.8	16	0.01
KL26-03	0	2.7	0.6	6000	0.19	1.6	2000	22	15	8	2	18	0.4	7.0	18	0.01
KL26-03	2.7	5.5	0.015	150	0.01	0.1	216	17	9	1	0.01	2	0.6	2.8	34	0.01
KL26-03	5.5	8.6	0.0384	384	0.05	0.1	100	17	9	1	0.01	1	1	1.8	23	0.01
KL26-03	8.6	11.7	0.0071	71	0.01	0.1	22	30	5	1	0.01	1	0.2	1.0	40	0.01
KL26-03	11.7	14.7	0.0045	45	0.03	0.1	120	38	6	1	0.01	1	1	1.5	29	0.01
KL26-03	14.7	17.7	0.0212	212	0.01	0.1	22	13	4	1	0.01	2	0.3	0.6	76	0.01
KL26-03	17.7	20.7	0.016	160	0.01	0.1	23	13	3	1	0.01	1	0.01	1.5	40	0.01
KL26-03	20.7	23.7	0.0044	44	0.01	0.1	27	18	2	1	0.01	1	0.01	1.0	30	0.01
KL26-03	23.7	26.7	0.0034	34	0.01	0.1	274	201	3	1	0.01	1	0.7	3.0	25	0.01
KL26-03	26.7	29.4	0.0099	99	0.01	0.7	1380	1080	8	1	0.01	3	2	3.8	39	0.01
KL26-03	29.4	32.7	0.008	80	0.01	0.1	132	213	11	4	1	4	1	1.5	77	0.01
KL26-03	32.7	35.7	0.58	5800	0.3	2.6	253	241	32	30	3	13	1.9	6.3	76	0.01
KL26-03	35.7	40.2	0.0342	342	0.1	15.6	11600	5900	41	10	4	1	9.4	15.6	19	0.01
KL26-03	40.2	43.2	0.15	1500	0.56	54	25500	43500	100	157	54	5	52	34.5	52	0.2
KL26-03	43.2	46.2	0.0069	69	0.22	4.2	126	3150	30	10	4	2	2.9	4.0	31	0.01
KL26-03	46.2	49.2	0.0061	61	0.08	1.9	181	3000	24	7	0.01	1	5.5	2.0	24	0.01
KL26-03	49.2	53.7	0.0141	141	0.13	6.1	119	2600	18	13	8	1	1.9	2.3	42	0.01
KL26-03	53.7	56.7	0.0119	119	0.01	1.5	800	2050	6	5	0.01	1	1.6	1.8	24	0.01
KL26-03	56.7	59.9	0.0185	185	0.04	6.3	560	4500	9	7	2	1	3.9	3.8	36	0.01
KL26-03	59.9	62.7	0.0115	115	0.01	1.7	96	600	5	6	1	1	1	0.0	26	0.01
KL26-03	62.7	65.7	0.0058	58	0.01	1.6	116	368	11	2	0.01	2	2.7	0.5	20	0.01
KL26-03	65.7	68.7	0.008	80	0.23	6.7	1600	2400	24	5	12	2	9	4.0	20	0.15
KL26-03	68.7	71.7	0.0053	53	0.04	7.2	1020	5500	20	11	10	1	5.3	3.5	11	0.01
KL26-03	71.7	74.2	0.0095	95	0.07	28.4	1920	11900	25	65	6	1	11.7	1.0	17	0.01
KL26-03	74.2	76.2	0.0055	55	0.03	5.9	820	1430	16	5	0.01	1	5.6	0.5	17	0.01
KL26-03	76.2	79.2	0.0065	65	0.04	11	860	1540	18	8	0.01	1	5.4	2.3	22	0.01
KL26-03	79.2	82.2	0.0026	26	0.02	10.7	940	1860	6	2	0.01	1	3.6	0.8	25	0.01
KL26-03	82.2	85.2	0.0067	67	0.01	19	1680	1770	15	5	1	1	10.4	3.5	20	0.01
KL26-03	85.2	88.2	0.0009	9	0.01	1.7	176	254	5	7	0.01	1	1.4	0.0	16	0.01
KL26-03	88.2	90.7	0.001	10	0.01	1.5	440	680	2	1	0.01	1	0.9	0.0	17	0.01
KL26-03	90.7	93.7	0.0012	12	0.01	1.4	350	770	4	1	0.01	1	1	0.0	22	0.01
KL26-03	93.7	96.8	0.0018	18	0.02	3.2	930	2800	2	2	1	1	1.4	0.5	16	0.01
KL26-03	96.8	99.8	0.0017	17	0.01	1.1	386	590	3	1	0.01	1	1.4	0.0	24	0.01
KL26-03	99.8	103.2	0.0005	5	0.01	0.6	129	246	2	1	0.01	1	0.6	0.0	24	0.01
KL26-03	103.2	105.6	0.0016	16	0.01	2.2	730	1060	4	1	0.01	1	0.9	0.0	20	0.01
KL26-03	105.6	109.2	0.0007	7	0.01	0.8	85	168	2	1	0.01	1	0.2	0.0	26	0.01
KL26-03	109.2	112.2	0.0014	14	0.01	2.4	490	1300	4	1	0.01	1	1.4	0.8	25	0.01
KL26-03	112.2	116.2	0.0014	14	0.02	2.7	324	460	4	3	0.01	1	0.8	0.5	26	0.01
KL26-03	116.2	120.2	0.0025	25	0.01	6.4	540	630	8	5	0.01	1	1.7	0.8	25	0.01
KL26-03	120.2	125.7	0.0039	39	0.02	6.3	490	1460	11	33	0.01	1	2.5	1.3	27	0.01
KL26-03	125.7	128.7	0.0011	11	0.01	1.7	176	278	11	4	0.01	1	0.4	0.0	25	0.01
KL26-03	128.7	131.7	0.0007	7	0.01	1.5	184	300	2	30	0.01	1	0.5	0.5	28	0.01
KL26-03	131.7	134.7	0.0007	7	0.01	1.1	148	230	1	11	0.01	1	0.3	1.0	28	0.01
KL26-03	134.7	137.7	0.0012	12	0.01	1.2	207	389	5	11	0.01	2	0.7	0.5	14	0.01
KL26-03	137.7	140.2	0.0013	13	0.01	1.7	310	346	7	14	0.01	2	1	1.2	14	0.01
KL26-03	140.2	143.4	0.002	20	0.01	2	306	223	8	19	0.01	1	1.8	0.5	13	0.01
KL26-03	143.4	147.5	0.0009	9	0.01	1.6	393	520	4	9	0.01	1	0.7	0.7	20	0.01
KL26-03	147.5	150.9	0.0023	23	0.01	3.1	1120	1020	5	6	1	1	2	1.0	15	0.01
KL26-03	150.9	155.5	0.001	10	0.01	1.1	253	321	2	2	0.01	1	0.5	0.8	15	0.01
KL26-03	155.5	159.6	0.0007	7	0.01	0.7	114	145	6	5	0.01	1	0.4	1.2	12	0.01
KL26-03	159.6	162.7	0.0006	6	0.01	0.1	95	129	2	4	0.01	1	0.01	1.0	14	0.01
KL26-03	162.7	165.7	0.0019	19	0.01	4.4	1280	1420	7	3	0.01	1	3	4.1	15	0.01
KL26-03	165.7	168.2	0.0005	5	0.01	0.7	83	132	1	1	0.01	1	0.7	0.0	13	0.01
KL26-03	168.2	170.7	0.0021	21	0.01	0.9	81	136	3	1	0.01	1	0.01	0.6	21	0.01
KL26-03	170.7	173.7	0.0014	14	0.01	1.2	640	270	3	1	0.01	1	0.01	1.0	17	0.01
KL26-03	173.7	176.7	0.0007	7	0.01	0.1	123	100	2	3	0.01	1	0.01	0.7	16	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL26-03	176.7	179.7	0.0014	14	0.01	0.1	112	141	2	1	0.01	1	0.01	1.0	16	0.01
KL26-03	179.7	182.7	0.0016	16	0.01	0.7	230	276	2	3	0.01	1	0.01	1.5	15	0.01
KL26-03	182.7	185.7	0.0008	8	0.03	0.1	223	160	3	6	0.01	3	0.01	1.4	19	0.01
KL26-03	185.7	188.7	0.0004	4	0.01	0.8	470	336	2	4	0.01	3	0.01	1.5	10	0.01
KL26-03	188.7	191.5	0.0009	9	0.01	0.1	85	180	2	4	0.01	1	0.01	0.5	14	0.01
KL26-03	191.5	195.2	0.0011	11	0.04	1.1	480	800	4	2	0.01	1	1.1	0.5	10	0.01
KL26-03	195.2	198.4	0.0024	24	0.01	1.7	960	940	4	7	3	1	0.9	3.8	16	0.01
KL26-03	198.4	200.7	0.0078	78	0.03	2.4	510	1300	21	13	2	4	1.5	7.3	29	0.01
KL26-03	200.7	203.7	0.0055	55	0.04	5.4	2600	7000	13	9	4	1	3.7	20.8	20	0.01
KL26-03	203.7	206.7	0.0031	31	0.02	1.6	1470	1450	12	8	1	1	0.8	10.0	19	0.01
KL26-03	206.7	209.7	0.013	130	0.04	7.8	5100	6000	16	13	17	1	2	56.2	28	0.01
KL26-03	209.7	212.7	0.0071	71	0.05	2.2	1400	3000	10	14	2	1	1.6	14.8	23	0.01
KL26-03	212.7	215.7	0.019	190	0.03	3	1430	3200	12	7	10	1	1.4	58.2	25	0.01
KL26-03	215.7	218.7	0.008	80	0.02	0.9	460	860	15	40	2	1	1.2	9.3	18	0.01
KL26-03	218.7	221.7	0.0245	245	0.04	1.6	2500	2400	18	20	2	1	1.4	12.3	25	0.01
KL26-03	221.7	224.7	0.06	600	0.31	5.1	4800	15000	26	80	6	1	0.9	40.5	15	0.01
KL26-03	224.7	227.4	0.158	1580	0.21	15.7	21100	30100	38	95	26	4	8.6	57.0	29	0.01
KL26-03	227.4	230.7	0.51	5100	0.36	41	20700	27000	27	1410	510	11	3.7	131.0	99	0.01
KL26-03	230.7	233.7	0.0356	356	0.07	1.6	580	340	3	2075	16	1	2.3	12.8	76	0.01
KL26-03	233.7	236.7	0.0193	193	0.04	0.8	91	149	3	1040	5	1	0.01	10.4	51	0.01
KL26-03	236.7	239.7	0.025	250	0.04	0.8	460	225	10	670	156	1	0.01	6.5	68	0.01
KL26-03	239.7	242.7	0.146	1460	0.17	197	54400	26200	29	112	1370	40	3.6	300.0	36	0.01
KL26-03	242.7	245.7	0.074	740	0.06	2.6	11800	610	13	73	300	7	0.5	17.3	29	0.01
KL26-03	245.7	248.7	0.053	530	0.08	1.9	9400	168	31	157	86	6	2.7	9.3	34	0.01
KL26-03	248.7	251.7	0.29	2900	1.69	9.6	28400	590	38	200	670	14	1.8	22.5	48	0.01
KL26-03	251.7	254.7	0.76	7600	1.24	4	26000	86	27	220	72	20	1.1	40.7	25	0.01
KL26-03	254.7	257.7	0.94	9400	1.44	3.8	11600	61	29	150	48	17	0.3	22.8	27	0.01
KL26-03	257.7	260.7	0.64	6400	1.37	9.3	14500	310	16	130	260	24	0.01	60.2	29	0.01
KL26-03	260.7	263.7	0.95	9500	1.8	1.4	630	37	19	260	8	16	0.2	14.8	25	0.01
KL26-03	263.7	266.7	0.254	2540	0.22	0.6	113	53	27	990	5	4	0.01	6.0	54	0.01
KL26-03	266.7	269.6	0.245	2450	0.14	0.7	258	95	16	3175	6	7	0.3	10.6	63	0.01
KL26-03	269.6	272.6	0.433	4330	0.43	1.1	293	22	18	680	2	14	0.01	7.3	39	0.01
KL26-03	272.6	274.2	0.69	6900	0.64	5	52400	15	8	14	7	112	0.01	21.5	38	0.01
KL26-03	274.2	277.2	0.66	6600	0.47	4.9	1700	20	20	57	3	82	0.01	14.8	25	0.01
KL26-03	277.2	280.2	1.66	16600	0.93	5.4	510	10	6	850	0.01	38	0.01	17.0	24	0.01
KL26-03	280.2	283.2	2.23	22300	1.12	5.6	151	14	5	376	0.01	53	1.2	21.0	26	0.01
KL26-03	283.2	286.2	1.12	11200	0.8	1.5	440	12	11	110	1	38	0.01	11.3	22	0.01
KL26-03	286.2	289.2	0.4	4000	0.46	1.1	277	22	11	81	1	30	2.5	6.8	22	0.01
KL26-03	289.2	292.4	0.512	5120	0.53	0.5	269	80	13	34	1	39	2	6.3	22	0.01
KL26-03	292.4	295.2	0.41	4100	0.45	0.9	183	14	6	46	2	35	1	9.8	28	0.01
KL26-03	295.2	297.8	0.124	1240	0.39	0.1	274	174	11	10	1	24	0.8	2.3	20	0.01
KL26-03	297.8	301	0.83	8300	1.07	1.3	151	21	2	276	3	30	0.4	9.0	33	0.01
KL26-03	301	304.2	0.78	7800	1.11	1.1	7200	16	4	47	6	44	0.6	10.3	24	0.01
KL26-03	304.2	307.2	0.58	5800	1.63	3.8	69000	66	7	18	7	69	0.01	23.0	32	0.01
KL26-03	307.2	310.2	0.36	3600	0.61	0.6	250	18	10	50	1	28	0.2	13.0	36	0.01
KL26-03	310.2	313.2	0.8	8000	0.79	1.1	490	12	20	640	2	52	0.6	13.5	35	0.01
KL26-03	313.2	316.2	4.58	45800	1.63	4.2	124	143	2	31	1	35	0.8	11.3	30	0.01
KL26-03	316.2	319.2	3.78	37800	2.13	6.1	100	720	2	7	3	37	0.7	11.3	86	0.01
KL26-03	319.2	320.8	2.77	27700	1.32	2.9	440	23	6	36	2	29	1	11.0	106	0.01
KL26-03	320.8	324.5	0.84	8400	0.47	3.4	358	275	34	155	2	30	1.9	7.0	101	0.01
KL26-03	324.5	326.7	1.53	15300	0.84	2.9	210	26	3	2300	1	34	0.01	8.0	87	0.01
KL26-03	326.7	329.7	1.08	10800	0.67	1.2	75	34	1	260	0.01	27	0.01	3.8	126	0.01
KL26-03	329.7	332.7	1.14	11400	0.63	0.9	74	23	5	260	0.01	18	0.3	4.3	143	0.01
KL26-03	332.7	335.7	1.05	10500	0.54	2.2	202	387	38	270	0.01	17	20	4.8	102	0.01
KL26-03	335.7	338.7	1.13	11300	0.73	1.7	62	27	2	110	1	27	0.2	4.8	118	0.01
KL26-03	338.7	341.4	1.07	10700	0.55	1.9	50	41	3	217	1	17	0.01	5.8	126	0.01
KL26-03	341.4	343	1.74	17400	0.37	4.2	700	220	370	228	1	17	20	6.2	153	0.43
KL26-03	343	346.2	1.21	12100	0.74	3.1	79	39	38	190	1	24	4	8.5	124	0.01
KL26-03	346.2	349.2	1.06	10600	0.64	1.3	63	15	2	110	1	20	0.5	6.0	80	0.01
KL26-03	349.2	352.2	0.91	9100	0.65	2.2	341	209	14	53	2	18	2.4	6.3	116	0.01
KL26-03	352.2	355.2	1.02	10200	1.1	4.4	800	210	5	60	1	14	0.5	8.5	178	0.01
KL26-03	355.2	358.2	1.03	10300	0.38	1.5	73	15	3	60	1	16	0.01	5.5	131	0.01
KL26-03	358.2	361.2	0.82	8200	0.49	8.8	430	288	200	130	1	13	9.5	9.5	156	0.11

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL26-03	361.2	364.2	0.9	9000	0.62	1.3	241	98	19	76	1	12	3	6.7	150	0.01
KL26-03	364.2	365.7	0.91	9100	0.58	1	57	17	3	40	2	11	0.2	6.8	135	0.01
KL26-03	365.7	368.6	1.06	10600	1.37	5.4	346	338	28	59	2	11	5.9	11.9	188	0.01
KL26-03	368.6	371.6	1.22	12200	0.84	2.2	75	60	3	270	2	11	0.01	6.3	136	0.01
KL26-03	371.6	374.6	1.44	14400	0.92	2.3	76	46	5	120	2	16	0.01	7.0	112	0.01
KL26-03	374.6	377.6	1.4	14000	0.93	3	73	33	2	61	2	13	0.01	6.4	132	0.01
KL26-03	377.6	380.6	1.07	10700	0.77	2.7	95	15	1	130	1	16	0.2	5.3	137	0.01
KL26-03	380.6	383.6	0.97	9700	0.84	2	84	35	3	34	1	13	0.01	5.2	119	0.01
KL26-03	383.6	386.6	0.86	8600	0.61	1.8	66	21	2	72	1	13	0.4	4.3	109	0.01
KL26-03	386.6	389.6	1.03	10300	0.63	2.1	58	18	3	254	1	15	0.3	4.3	93	0.01
KL26-03	389.6	392.6	0.53	5300	0.33	1.7	1110	610	4	85	0.01	9	0.4	4.0	87	0.01
KL26-03	392.6	395.6	0.8	8000	0.42	1.7	71	16	2	72	1	20	0.01	3.0	111	0.01
KL26-03	395.6	398.6	0.88	8800	0.49	1.9	127	15	6	66	0.01	18	0.01	4.3	95	0.01
KL26-03	398.6	401.6	1.37	13700	0.54	2.8	249	101	9	17	1	16	0.6	5.2	97	0.01
KL26-03	401.6	404.6	1.47	14700	0.81	2.9	176	38	15	149	1	22	10.6	4.5	92	0.01
KL26-03	404.6	407.6	0.78	7800	0.33	2.4	149	75	8	59	0.01	17	4.9	5.3	93	0.01
KL26-03	407.6	409.1	1.07	10700	0.48	2.1	161	22	4	43	0.01	19	0.5	7.0	75	0.01
KL26-03	409.1	413.6	0.85	8500	0.43	2.9	402	178	110	72	1	14	45	6.3	266	0.01
KL26-03	413.6	416.6	0.76	7600	0.18	2.1	289	110	24	35	1	10	1.7	5.8	366	0.01
KL26-03	416.6	419.6	0.78	7800	0.14	12.5	1620	1820	410	53	5	6	52	6.4	59	0.1
KL26-03	419.6	422.6	1.02	10200	0.14	9	11000	2700	220	65	5	6	21	7.0	379	0.1
KL26-03	422.6	425.4	0.87	8700	0.24	3.9	640	278	140	29	2	9	3.4	7.5	347	0.01
KL26-03	425.4	427.4	0.75	7500	0.34	1.7	50	29	16	49	1	14	1.7	4.8	52	0.01
KL26-03	427.4	430.5	1.05	10500	1.14	2.6	64	65	18	20	3	10	1.6	4.8	270	0.01
KL26-03	430.5	433.6	0.89	8900	0.52	1.7	87	86	18	18	1	10	1	7.9	307	0.01
KL26-03	433.6	436.7	1.89	18900	1.73	4.6	53	89	12	27	4	11	0.7	9.5	182	0.01
KL26-03	436.7	439.8	1.05	10500	0.22	2.7	186	142	140	27	2	4	9.8	9.5	42	0.01
KL26-03	439.8	442.9	0.76	7600	0.12	8	590	338	450	28	3	4	80	4.5	45	0.01
KL26-03	442.9	445	1	10000	0.41	62	1820	700	1210	43	7	3	1750	6.5	186	0.31
KL26-03	445	446.6	0.95	9500	1.5	63	6600	3300	2800	3	41	1	300	38.0	104	0.81
KL26-03	446.6	449.2	1.41	14100	0.25	17.1	3100	930	1230	40	7	4	178	6.5	51	0.25
KL26-03	449.2	452.2	1.32	13200	0.22	3.5	385	233	160	40	1	3	9.7	8.2	41	0.01
KL26-03	452.2	455.7	0.9	9000	0.28	3.1	480	243	77	45	1	10	4.2	7.5	38	0.01
KL26-03	455.7	458.7	0.83	8300	0.31	2.7	150	89	36	56	1	8	2.8	5.0	57	0.01
KL26-03	458.7	461.8	1.03	10300	0.34	5.8	480	225	420	19	2	8	36	5.0	286	0.01
KL26-03	461.8	464.6	1.06	10600	0.3	7.6	2100	1200	1070	25	2	3	46	5.0	51	0.14
KL26-03	464.6	467.6	0.9	9000	0.35	16.7	1400	4800	540	15	3	3	400	7.0	233	0.16
KL26-03	467.6	470.6	1	10000	0.79	4.6	245	163	81	15	3	9	19.4	6.0	189	0.01
KL26-03	470.6	473.6	1.3	13000	0.74	21.5	1090	600	1090	18	5	7	570	8.5	296	0.29
KL26-03	473.6	476.6	0.86	8600	0.65	2.1	92	37	17	28	1	6	2.6	5.3	281	0.01
KL26-03	476.6	479.6	0.87	8700	0.51	2.2	120	38	10	47	1	11	0.6	5.5	273	0.01
KL26-03	479.6	482.6	1.03	10300	0.75	2.4	720	182	53	17	1	9	8.5	6.3	72	0.01
KL26-03	482.6	485.6	1.02	10200	0.79	1.7	39	25	9	24	1	8	1.1	6.8	253	0.01
KL26-03	485.6	488.6	0.74	7400	0.49	2.3	110	42	15	23	1	7	2.3	4.9	138	0.01
KL26-03	488.6	491.6	0.81	8100	0.48	2.8	1410	860	46	29	0.01	8	24	4.8	126	0.1
KL26-03	491.6	494.6	0.74	7400	0.48	1.7	90	36	15	18	0.01	8	2.7	3.8	233	0.01
KL26-03	494.6	497.6	0.8	8000	0.45	1.8	46	10	4	10	0.01	9	0.9	5.9	262	0.01
KL26-03	497.6	500.6	0.64	6400	0.37	1.7	137	57	4	29	0.01	9	0.8	4.3	252	0.01
KL26-03	500.6	503.6	0.63	6300	0.38	1.8	28	13	3	24	0.01	9	0.4	4.8	289	0.01
KL26-03	503.6	506.6	0.62	6200	0.24	3.3	540	184	240	27	1	9	70	5.0	214	0.1
KL26-03	506.6	509.6	0.57	5700	0.32	2.4	121	45	18	24	0.01	10	2.5	5.5	58	0.01
KL26-03	509.6	512.6	0.006	60	0.11	2.5	41	250	22	12	0.01	1	3.3	1.0	126	0.01
KL26-03	512.6	515.6	0.37	3700	0.13	3.8	850	500	400	15	1	5	20.4	3.5	177	0.01
KL26-03	515.6	518.6	0.42	4200	0.14	3.6	600	425	100	28	1	7	4.7	4.3	156	0.1
KL26-03	518.6	521.6	0.53	5300	0.13	3.8	670	296	84	17	1	5	12	5.3	145	0.12
KL26-03	521.6	524.6	0.46	4600	0.28	2.2	126	98	25	14	0.01	6	2.5	4.0	164	0.01
KL26-03	524.6	527.6	0.419	4190	0.19	1.2	31	10	3	55	0.01	6	0.2	3.3	200	0.01
KL26-03	527.6	530.6	0.58	5800	0.25	2	135	48	6	27	1	8	1.1	3.0	171	0.01
KL26-03	530.6	533.6	0.433	4330	0.26	1.1	62	16	3	15	0.01	8	0.01	3.3	172	0.01
KL26-03	533.6	536.1	0.725	7250	0.28	1.4	71	12	1	13	0.01	10	0.01	4.5	243	0.01
KL26-03	536.1	539.6	0.2	2000	0.09	0.9	248	94	8	63	0.01	7	0.3	1.1	155	0.01
KL26-03	539.6	542.6	0.467	4670	0.27	1.3	43	13	11	97	0.01	8	0.5	4.5	155	0.01
KL26-03	542.6	545.6	0.302	3020	0.09	3.5	295	208	100	17	1	6	10.6	4.3	186	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL26-03	545.6	548.6	0.266	2660	0.1	1	37	15	3	58	0.01	6	0.01	1.8	169	0.01
KL26-03	548.6	551.6	0.405	4050	0.13	1.4	1030	330	6	33	0.01	7	0.3	4.9	245	0.01
KL26-03	551.6	554.6	0.5	5000	0.32	1.1	58	16	4	48	0.01	7	0.2	3.8	198	0.01
KL26-03	554.6	557.6	0.392	3920	0.17	0.9	55	12	6	49	0.01	6	0.3	2.5	256	0.01
KL26-03	557.6	560.6	0.71	7100	0.48	1.3	70	13	5	15	0.01	8	0.2	4.0	246	0.01
KL26-03	560.6	563.6	0.32	3200	0.12	1	46	9	2	24	0.01	8	0.01	3.3	176	0.01
KL26-03	563.6	566.6	0.265	2650	0.13	0.9	36	16	1	18	0.01	6	0.01	2.7	161	0.01
KL26-03	566.6	569.6	0.47	4700	0.1	3.1	228	107	47	27	0.01	7	40	5.5	166	0.01
KL26-03	569.6	572.6	0.29	2900	0.05	3.1	800	385	140	47	0.01	8	38	6.4	170	0.01
KL26-03	572.6	575.6	0.28	2800	0.09	2	336	114	20	16	0.01	6	2.8	3.8	148	0.01
KL26-03	575.6	578.6	0.361	3610	0.16	1.2	61	26	4	25	0.01	5	0.01	4.0	157	0.01
KL26-03	578.6	581.6	0.376	3760	0.26	1.4	84	40	8	56	1	7	2.8	4.8	255	0.01
KL26-03	581.6	584.6	1.05	10500	0.6	4.5	560	171	7	207	1	9	2.7	5.5	213	0.01
KL26-03	584.6	587.6	0.426	4260	0.21	1.6	220	125	3	24	1	8	0.8	6.7	259	0.01
KL26-03	587.6	590.6	0.34	3400	0.1	3.1	720	600	19	23	0.01	7	19.8	4.0	185	0.01
KL26-03	590.6	593.6	0.21	2100	0.07	4.6	660	1830	52	25	4	5	16.5	4.0	158	0.1
KL26-03	593.6	596.6	0.36	3600	0.06	1.9	226	91	17	24	0.01	8	2.3	4.8	215	0.01
KL26-03	596.6	599.6	0.61	6100	0.07	44	6000	6100	780	40	3	6	1000	3.5	216	0.3
KL26-03	599.6	602.6	0.505	5050	0.1	21.6	3890	1780	520	22	3	4	380	5.3	260	0.27
KL26-03	602.6	605.6	0.75	7500	0.28	28.3	640	840	110	42	7	8	86	5.3	375	0.01
KL26-03	605.6	608.6	0.501	5010	0.23	3.4	185	120	27	15	1	8	2.6	4.5	227	0.01
KL26-03	608.6	611.6	0.18	1800	0.06	8.7	810	402	130	31	6	5	20.4	4.3	228	0.11
KL26-03	611.6	614.6	0.44	4400	0.08	2.1	129	112	12	24	1	6	2.5	5.3	348	0.01
KL26-03	614.6	617.6	0.23	2300	0.14	1	28	16	10	37	0.01	6	0.5	2.0	260	0.01
KL26-03	617.6	620.6	0.354	3540	0.2	0.7	40	15	2	54	0.01	9	0.01	3.5	243	0.01
KL26-03	620.6	623	0.41	4100	0.26	0.8	43	36	2	32	0.01	8	1.4	4.5	231	0.01
KL26-03	623	626.1	0.473	4730	0.16	0.9	28	16	2	61	1	7	0.01	4.6	266	0.01
KL26-03	626.1	629.2	0.304	3040	0.16	0.7	36	18	2	34	0.01	7	0.4	3.8	216	0.01
KL26-03	629.2	632.6	0.468	4680	0.44	0.8	40	10	1	28	0.01	7	0.4	4.3	296	0.01
KL26-03	632.6	635.6	0.323	3230	0.23	0.7	32	12	4	36	0.01	8	0.2	1.3	427	0.01
KL26-03	635.6	638.6	0.32	3200	0.08	0.8	54	24	13	26	0.01	6	0.2	4.3	300	0.01
KL26-03	638.6	641.6	0.35	3500	0.09	3.6	258	118	170	24	1	7	14.1	5.0	268	0.01
KL26-03	641.6	644.6	0.4	4000	0.06	3	228	118	100	53	1	8	5.7	5.8	236	0.01
KL26-03	644.6	647.6	0.37	3700	0.08	1.6	137	61	34	71	0.01	8	6.9	4.6	281	0.01
KL26-03	647.6	650.6	0.302	3020	0.09	1.2	304	123	60	60	0.01	7	4.8	4.5	203	0.01
KL26-03	650.6	653.6	0.242	2420	0.12	0.7	140	52	40	48	0.01	6	3.8	3.5	281	0.01
KL26-03	653.6	656.6	0.31	3100	0.14	0.7	42	20	2	77	0.01	7	0.3	4.0	312	0.01
KL26-03	656.6	659.6	0.22	2200	0.13	0.6	32	16	2	36	0.01	7	0.4	2.5	210	0.01
KL26-03	659.6	662.6	0.23	2300	0.09	0.6	27	13	2	33	0.01	6	0.4	3.0	156	0.01
KL26-03	662.6	665.2	0.23	2300	0.1	1.6	40	29	110	43	1	6	10.8	4.4	269	0.01
KL26-03	665.2	668.4	0.21	2100	0.07	1	82	72	19	24	0.01	6	0.5	3.8	167	0.01
KL26-03	668.4	671.5	0.21	2100	0.05	2.5	105	132	120	64	3	7	8	4.0	162	0.01
KL26-03	671.5	674.6	0.22	2200	0.03	1.4	124	65	57	75	1	7	1.2	3.5	122	0.01
KL26-03	674.6	677.6	0.436	4360	0.06	1	48	15	5	63	0.01	10	0.01	6.0	245	0.01
KL26-03	677.6	680.6	0.55	5500	0.07	1.9	68	31	28	89	0.01	9	1.6	4.8	261	0.01
KL26-03	680.6	683.3	0.37	3700	0.1	0.9	43	14	6	52	0.01	11	0.2	4.6	198	0.01
KL26-03	683.3	686.5	0.48	4800	0.18	1	28	9	6	43	0.01	12	0.01	5.8	245	0.01
KL26-03	686.5	689.6	0.67	6700	0.28	1.8	26	10	2	29	0.01	11	0.01	6.0	407	0.01
KL26-03	689.6	692.6	0.466	4660	0.14	1.1	61	26	16	27	0.01	7	0.01	4.8	242	0.01
KL26-03	692.6	695.6	0.37	3700	0.08	1	44	20	8	564	0.01	8	0.4	4.5	410	0.01
KL26-03	695.6	698.6	0.63	6300	0.4	1.2	46	11	0.01	60	0.01	8	0.01	4.8	170	0.01
KL26-03	698.6	701.6	1.24	12400	1	1.6	148	11	0.01	136	1	34	0.01	14.8	21	0.01
KL26-03	701.6	704.6	0.21	2100	0.16	0.1	126	8	1	18	0.01	27	0.01	1.0	42	0.01
KL26-03	704.6	707.6	0.314	3140	0.14	0.6	143	8	2	23	0.01	26	0.01	4.5	48	0.01
KL26-03	707.6	710.6	0.75	7500	0.37	1.8	192	8	3	27	0.01	30	0.4	7.9	71	0.01
KL26-03	710.6	712.8	0.67	6700	0.28	1.6	249	10	1	8	0.01	27	0.01	6.0	84	0.01
KL26-03	712.8	715.6	0.382	3820	0.26	1.2	299	7	3	9	0.01	32	0.4	3.3	83	0.01
KL26-03	715.6	718.6	0.53	5300	0.43	2	262	9	2	4	3	31	0.4	5.8	32	0.01
KL26-03	718.6	721.2	0.56	5600	0.22	1.5	192	14	3	11	1	26	0.01	4.8	43	0.01
KL26-03	721.2	724.3	0.75	7500	0.28	2.1	165	6	1	5	0.01	19	0.01	4.0	57	0.01
KL26-03	724.3	726.8	0.11	1100	0.04	0.5	57	5	3	42	0.01	12	0.01	1.2	30	0.01
KL26-03	726.8	728.6	1.48	14800	0.54	3.9	250	6	9	67	0.01	38	0.01	18.0	45	0.01
KL26-03	728.6	731.6	0.54	5400	0.32	2.1	304	9	6	10	0.01	25	0.01	11.4	36	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL26-03	731.6	734.6	0.54		5400	0.36	2.1	194	7	5	29	0.01	20	0.3	12.5	32	0.01
KL26-03	734.6	737.6	0.07		700	0.02	0.1	55	8	1	10	0.01	18	0.01	1.3	28	0.01
KL26-03	737.6	740.6	0.117		1170	0.05	0.1	53	8	2	19	0.01	15	0.01	0.7	21	0.01
KL26-03	740.6	743.1	0.157		1570	0.12	0.1	47	13	2	30	0.01	8	0.4	1.2	30	0.01
KL26-03	743.1	746.2	0.32		3200	0.13	1	112	11	0.01	11	0.01	34	0.8	1.8	43	0.01
KL26-03	746.2	749.3	0.25		2500	0.11	0.1	113	7	0.01	27	0.01	18	0.3	3.0	40	0.01
KL26-03	749.3	752.3	0.35		3500	0.12	0.6	183	44	5	27	0.01	16	0.6	3.5	31	0.01
KL26-03	752.3	755.4	0.414		4140	0.15	0.8	179	43	1	60	0.01	16	0.3	4.5	28	0.01
KL26-03	755.4	758.5	0.36		3600	0.1	0.1	72	12	0.01	60	0.01	16	0.2	2.8	28	0.01
KL26-03	758.5	761.6	0.23		2300	0.09	0.1	43	8	0.01	24	0.01	12	0.4	4.5	30	0.01
KL26-03	761.6	764.6	0.093		930	0.06	0.1	15	6	0.01	36	0.01	1	0.01	0.0	13	0.01
KL26-03	764.6	767.6	0.134		1340	0.05	0.1	80	6	0.01	16	0.01	21	0.01	1.2	26	0.01
KL26-03	767.6	770.6	0.131		1310	0.08	0.1	64	7	0.01	16	0.01	10	0.01	1.1	38	0.01
KL26-03	770.6	773.6	0.149		1490	0.09	0.1	68	7	0.01	22	0.01	10	0.01	1.8	36	0.01
KL26-03	773.6	775.1	0.102		1020	0.1	0.1	72	7	2	25	0.01	10	0.01	1.5	34	0.01
KL26-04	0	2.9	0.0041		41	0.01	0.1	83	70	5	3	0.01	1	0.4	1.5	31	0.01
KL26-04	2.9	5.9	0.0028		28	0.01	0.1	37	19	8	2	0.01	1	1.1	3.7	24	0.01
KL26-04	5.9	8.9	0.0021		21	0.01	0.1	19	14	5	1	0.01	1	0.4	2.0	38	0.01
KL26-04	8.9	11.5	0.0032		32	0.02	0.1	51	34	10	5	0.01	1	1.4	3.5	38	0.01
KL26-04	11.5	14.6	0.0042		42	0.01	0.1	22	29	4	3	0.01	1	0.7	2.0	44	0.01
KL26-04	14.6	17.3	0.0036		36	0.01	0.1	21	13	4	13	0.01	1	1.7	2.3	47	0.01
KL26-04	17.3	20.4	0.0027		27	0.01	0.1	26	10	5	2	0.01	1	0.5	2.7	36	0.01
KL26-04	20.4	23.4	0.0024		24	0.01	0.1	53	17	5	1	0.01	1	0.4	1.6	55	0.01
KL26-04	23.4	25.5	0.0024		24	0.01	0.1	28	17	7	2	0.01	1	0.5	1.7	104	0.01
KL26-04	25.5	29.1	0.0019		19	0.01	0.1	46	23	8	3	1	2	3.8	5.0	138	0.01
KL26-04	29.1	30.2	0.0013		13	0.04	0.5	35	102	28	2	0.01	8	1.4	3.3	90	0.01
KL26-04	30.2	35.9	0.066		660	0.36	36.1	35700	23400	120	8	14	1	26	120.0	55	0.29
KL26-04	35.9	37.5	0.0033		33	0.07	5.1	320	1640	19	12	6	1	3.2	3.6	177	0.01
KL26-04	37.5	40.4	0.009		90	0.07	8.6	650	5000	43	13	5	1	7.5	21.2	46	0.01
KL26-04	40.4	43.4	0.0024		24	0.12	1.3	129	640	24	20	0.01	1	4.2	3.2	164	0.01
KL26-04	43.4	46.1	0.0021		21	0.06	1.6	141	1570	20	7	0.01	1	2.3	2.3	201	0.01
KL26-04	46.1	49.4	0.0024		24	0.02	1.1	95	1020	6	8	0.01	1	1.9	1.5	232	0.01
KL26-04	49.4	52.4	0.0023		23	0.02	1.2	85	730	18	12	0.01	1	4.4	0.0	117	0.01
KL26-04	52.4	54.2	0.0015		15	0.01	2.3	210	1720	10	10	0.01	1	3.7	1.2	124	0.01
KL26-04	54.2	57.7	0.0024		24	0.04	2.3	212	1610	9	6	0.01	1	3.6	2.3	146	0.01
KL26-04	57.7	60.9	0.0025		25	0.01	1	95	730	9	8	0.01	1	2.5	0.6	112	0.01
KL26-04	60.9	63.9	0.0032		32	0.03	0.9	180	169	13	16	0.01	1	1.7	0.5	121	0.01
KL26-04	63.9	66.9	0.0033		33	0.04	2.3	161	1400	29	29	0.01	1	4	1.5	107	0.01
KL26-04	66.9	70	0.0019		19	0.02	1.3	105	238	27	7	0.01	1	2.8	0.6	38	0.01
KL26-04	70	74	0.0024		24	0.42	4.9	126	620	42	5	0.01	1	7.1	2.3	120	0.01
KL26-04	74	76.9	0.0015		15	0.03	1.8	180	730	7	7	1	1	1.4	1.7	35	0.01
KL26-04	76.9	79.7	0.0012		12	0.02	2.4	19	520	8	5	2	3	1	2.3	22	0.01
KL26-04	79.7	85.4	0.0013		13	0.06	1.6	380	175	9	8	1	1	1	2.0	21	0.01
KL26-04	85.4	89.9	0.003		30	0.08	6.6	490	2400	21	4	7	1	2.7	1.7	18	0.01
KL26-04	89.9	94.4	0.0008		8	0.11	1.9	357	288	3	2	0.01	1	1.3	2.0	23	0.01
KL26-04	94.4	98.9	0.0028		28	0.03	3.7	40	530	12	8	8	1	1.1	2.0	26	0.01
KL26-04	98.9	101.9	0.0127		127	0.03	2.2	402	9600	44	7	3	1	13.3	3.8	28	0.01
KL26-04	101.9	104.9	0.0013		13	0.01	0.8	35	186	6	1	0.01	1	0.7	0.0	26	0.01
KL26-04	104.9	107.9	0.0023		23	0.02	2.1	85	510	5	1	1	1	0.8	1.7	27	0.01
KL26-04	107.9	112.4	0.0024		24	0.01	2.1	23	230	8	1	1	1	0.9	3.0	25	0.01
KL26-04	112.4	116.9	0.0016		16	0.02	2.2	16	690	3	6	1	3	1.3	2.5	28	0.01
KL26-04	116.9	119.9	0.0015		15	0.01	1.2	33	322	2	5	1	1	3.5	1.0	32	0.01
KL26-04	119.9	124.4	0.0017		17	0.02	3	104	840	5	10	0.01	1	1.4	1.7	16	0.01
KL26-04	124.4	127.4	0.0014		14	0.02	3.4	202	440	15	24	0.01	1	0.4	0.9	17	0.01
KL26-04	127.4	130.4	0.0025		25	0.01	5.3	308	1620	5	5	2	1	2.4	2.3	17	0.01
KL26-04	130.4	133.4	0.0107		107	0.03	4.1	128	740	4	5	0.01	1	2.1	1.7	17	0.01
KL26-04	133.4	139.4	0.0015		15	0.01	4.1	85	720	3	5	0.01	1	1.3	2.3	16	0.01
KL26-04	139.4	142.4	0.0029		29	0.01	2.4	85	540	3	7	0.01	1	1	1.2	12	0.01
KL26-04	142.4	145.4	0.0014		14	0.01	1.6	132	210	1	7	0.01	1	0.8	0.7	14	0.01
KL26-04	145.4	148.4	0.0282		282	0.01	2	60	115	8	14	0.01	1	1.4	1.5	17	0.01
KL26-04	148.4	151.4	0.0134		134	0.01	3.3	280	355	9	7	1	1	0.9	1.7	16	0.01
KL26-04	151.4	154.4	0.0028		28	0.01	3.2	378	740	6	8	1	1	2.1	1.7	23	0.01
KL26-04	154.4	158.9	0.0021		21	0.01	2.2	440	480	2	8	1	1	0.6	0.7	21	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL26-04	158.9	161.9	0.0038		38	0.02	1.8	178	157	4	6	1	1	0.5	1.0	22	0.01
KL26-04	161.9	164.9	0.0012		12	0.01	1	55	131	4	10	1	1	0.5	0.5	13	0.01
KL26-04	164.9	167.9	0.0013		13	0.01	0.9	75	121	7	7	0.01	1	0.5	1.2	20	0.01
KL26-04	167.9	170.9	0.0013		13	0.01	0.8	56	46	5	8	0.01	1	0.6	1.0	17	0.01
KL26-04	170.9	173.6	0.0024		24	0.01	1.4	371	319	7	9	0.01	1	1.3	1.5	18	0.01
KL26-04	173.6	176.7	0.0019		19	0.01	1.3	480	336	7	11	0.01	1	1.2	1.5	17	0.01
KL26-04	176.7	179.9	0.0176		176	0.06	3.5	1540	1620	58	23	1	1	4.8	5.5	31	0.01
KL26-04	179.9	182.9	0.0131		131	0.08	2.6	840	950	28	13	2	1	4.2	3.5	30	0.01
KL26-04	182.9	185.9	0.0065		65	0.07	2.4	900	1650	18	13	0.01	1	2.7	2.3	23	0.01
KL26-04	185.9	188.9	0.0057		57	0.07	2.2	343	1840	13	26	7	1	0.8	3.3	20	0.01
KL26-04	188.9	191.9	0.02		200	0.18	5.1	3200	5200	28	73	12	2	4.3	7.0	26	0.11
KL26-04	191.9	194.4	0.0086		86	0.08	3.1	3400	3600	16	17	6	1	1.2	2.3	18	0.15
KL26-04	194.4	196.4	0.0188		188	0.08	3.2	1900	1150	32	120	56	1	3	7.0	23	0.01
KL26-04	196.4	199.2	0.047		470	0.11	9	3200	7000	38	32	38	1	2.7	13.6	28	0.13
KL26-04	199.2	201.4	0.29		2900	0.96	13.6	29900	5200	610	37	54	36	6.8	70.8	112	0.61
KL26-04	201.4	202.7	0.58		5800	1.96	9.6	47600	620	370	520	120	32	5	97.0	168	1.23
KL26-04	202.7	204.6	0.078		780	1.29	1.3	201	32	240	1320	28	9	6	21.0	177	0.45
KL26-04	204.6	208	0.095		950	0.96	1.4	166	76	260	2200	28	6	5.9	19.8	201	0.2
KL26-04	208	210.3	0.179		1790	0.49	1.9	67	27	54	3230	40	6	1.4	11.2	78	0.12
KL26-04	210.3	212.9	0.81		8100	2.4	8.9	241	40	260	2200	100	56	5	16.0	78	0.72
KL26-04	212.9	216.2	0.63		6300	4.32	3.5	398	50	630	2525	18	5	9.8	10.1	117	0.85
KL26-04	216.2	218.6	0.93		9300	1.15	3.2	167	18	49	223	9	7	1.2	10.5	92	0.1
KL26-04	218.6	221.1	0.48		4800	0.77	2.3	137	35	140	1365	2	11	1.6	14.3	57	0.18
KL26-04	221.1	223	0.59		5900	0.71	2.6	262	38	150	1910	6	7	1.5	8.7	51	0.32
KL26-04	223	225.1	0.53		5300	1.07	3.5	196	25	160	4810	5	19	1.5	13.5	68	0.18
KL26-04	225.1	227.9	0.34		3400	0.57	2.2	87	13	33	208	3	5	0.4	10.5	22	0.01
KL26-04	227.9	230.9	1.06		10600	1.37	4.7	358	21	130	370	3	11	0.4	19.5	57	0.12
KL26-04	230.9	232.7	0.26		2600	0.45	1.4	204	15	30	478	2	10	0.3	6.5	41	0.16
KL26-04	232.7	235.4	0.325		3250	1.09	1.8	313	63	280	234	3	9	1.7	10.0	65	0.34
KL26-04	235.4	238.1	1.36		13600	3.13	14.5	3500	134	290	125	10	81	2.5	29.5	97	0.49
KL26-04	238.1	241.3	2.08		20800	4.48	20	2100	152	120	166	10	49	2.6	23.0	100	0.19
KL26-04	241.3	244.5	0.245		2450	0.33	2.7	97	49	26	1125	6	8	1.1	17.0	122	0.01
KL26-04	244.5	247.4	0.46		4600	1.52	5.5	760	130	230	380	19	33	2.3	28.0	164	0.01
KL26-04	247.4	250.4	1.19		11900	1.71	10.2	365	48	48	370	21	12	0.8	11.5	136	0.01
KL26-04	250.4	253.4	1.77		17700	5.13	18.1	860	48	42	210	20	68	1.8	18.0	187	0.01
KL26-04	253.4	256.8	0.86		8600	1.19	10.3	3500	156	470	650	25	50	4.2	25.5	386	0.38
KL26-04	256.8	259.4	1.17		11700	1.29	6.7	3100	283	200	42	18	32	2.2	23.2	213	0.19
KL26-04	259.4	262.4	0.9		9000	0.83	5.7	2600	790	260	26	26	30	3.6	63.8	305	0.12
KL26-04	262.4	265.4	1.93		19300	2.17	13.4	8700	1400	34	15	64	30	4.5	38.2	194	0.1
KL26-04	265.4	268.4	1.28		12800	1.77	6.9	670	56	30	81	7	42	2.4	31.5	93	0.1
KL26-04	268.4	271.4	1.24		12400	3.29	9.1	1610	450	16	13	30	44	1.8	24.3	48	0.01
KL26-04	271.4	274.4	1.56		15600	3.11	9.4	9800	72	11	6	10	199	1.6	42.0	86	0.1
KL26-04	274.4	277.4	2.12		21200	2.32	6.7	254	96	5	63	1	81	0.8	34.0	115	0.01
KL26-04	277.4	280.4	2.04		20400	2.6	5.9	268	35	1	21	1	41	0.4	28.7	92	0.01
KL26-04	280.4	283.4	2.24		22400	2.53	5.8	198	31	30	40	0.01	83	0.4	15.2	209	0.01
KL26-04	283.4	286.4	2.83		28300	2.43	5.2	940	480	760	50	1	99	16.8	25.0	219	0.49
KL26-04	286.4	289.4	4.28		42800	2.68	3.6	269	24	29	231	0.01	86	0.4	26.0	213	0.01
KL26-04	289.4	292.4	4.31		43100	2.84	5.8	324	37	7	135	0.01	80	0.2	25.0	55	0.01
KL26-04	292.4	295.4	2.35		23500	1.87	3.1	137	12	0.01	291	0.01	74	0.01	15.5	34	0.01
KL26-04	295.4	298.4	3.17		31700	2.77	4.7	148	8	0.01	227	0.01	76	0.01	20.0	43	0.01
KL26-04	298.4	301.4	3.46		34600	2.61	6.6	700	600	3	256	0.01	75	0.01	21.5	45	0.01
KL26-04	301.4	304.4	3.21		32100	2.48	5.4	223	67	5	529	0.01	57	0.01	21.0	54	0.01
KL26-04	304.4	307.4	1.3		13000	1.09	2	104	10	0.01	260	0.01	52	0.01	9.8	38	0.01
KL26-04	307.4	310.4	3.67		36700	2.65	4.4	124	15	1	409	0.01	96	0.01	34.0	76	0.01
KL26-04	310.4	313.4	3.29		32900	2.59	5.8	266	72	3	354	0.01	75	0.01	18.5	40	0.01
KL26-04	313.4	316.4	1.93		19300	1.69	3.9	151	20	1	311	0.01	58	0.01	9.0	50	0.01
KL26-04	316.4	319.4	1.96		19600	2.03	3.7	121	9	0.01	52	0.01	45	0.01	6.5	78	0.01
KL26-04	319.4	322.4	1.69		16900	1.51	2.4	101	8	1	270	0.01	44	0.01	15.0	48	0.01
KL26-04	322.4	325.4	2.28		22800	3.05	6.2	590	2600	83	490	0.01	54	13.7	14.0	92	2.77
KL26-04	325.4	326.9	0.68		6800	0.77	3.4	196	22	18	98	3	53	0.9	13.7	60	0.01
KL26-04	326.9	329.9	1		10000	0.69	6.4	102	20	5	36	3	43	0.6	20.0	106	0.01
KL26-04	329.9	331.9	0.294		2940	0.29	2.1	64	21	4	648	9	11	0.2	13.7	121	0.01
KL26-04	331.9	334.4	0.32		3200	0.32	2.8	83	20	24	317	9	16	0.2	17.3	138	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL26-04	334.4	337.4	0.351	3510	0.39	2.1	60	14	20	286	6	38	0.3	17.5	87	0.01
KL26-04	337.4	340.4	2.03	20300	1.87	12.2	342	21	7	241	7	39	0.01	17.2	120	0.01
KL26-04	340.4	343.4	0.81	8100	1.08	5.5	117	21	15	736	13	14	0.2	11.7	134	0.01
KL26-04	343.4	346.4	1.56	15600	1.76	9.6	198	22	16	630	27	42	0.3	11.5	144	0.01
KL26-04	346.4	348.6	2.52	25200	3.6	17.5	650	18	20	180	8	57	0.01	23.5	148	0.01
KL26-04	348.6	350.9	3.52	35200	6.01	21.8	840	23	12	6	6	84	0.3	19.0	81	0.01
KL26-04	350.9	353.9	1.38	13800	2.14	8.9	257	18	18	36	7	48	0.2	17.7	161	0.01
KL26-04	353.9	356.9	4.52	45200	5.6	29.8	750	13	17	103	5	136	0.3	13.0	139	0.01
KL26-04	356.9	359.9	1.08	10800	1.15	7.7	145	19	19	102	6	22	0.2	10.5	114	0.01
KL26-04	359.9	362.9	2.34	23400	2.65	16.1	470	17	19	95	4	51	0.3	13.0	88	0.01
KL26-04	362.9	364.4	1.55	15500	2.13	10.2	232	20	12	136	4	55	0.01	18.7	177	0.01
KL26-04	364.4	367.4	3.8	38000	5.32	28.3	810	14	12	100	3	98	0.5	24.0	136	0.01
KL26-04	367.4	370.4	0.325	3250	0.47	2.4	55	17	11	189	21	10	0.2	13.3	103	0.01
KL26-04	370.4	373.4	0.266	2660	0.32	2	48	16	14	123	18	6	0.2	15.2	119	0.01
KL26-04	373.4	376.4	0.277	2770	0.33	2.1	47	18	19	171	15	10	0.3	24.9	133	0.01
KL26-04	376.4	379.4	0.202	2020	0.24	1.5	34	14	23	90	25	7	0.4	26.4	164	0.01
KL26-04	379.4	382.4	0.358	3580	0.47	2.4	40	15	25	270	37	12	0.7	19.2	76	0.01
KL26-04	382.4	385.4	0.361	3610	0.52	2.3	33	25	60	140	29	9	1.6	26.4	116	0.01
KL26-04	385.4	388.4	0.85	8500	0.79	4.4	50	17	32	41	16	18	0.9	19.5	53	0.01
KL26-04	388.4	391.4	2.59	25900	2.6	11.6	91	11	28	43	10	58	1	28.5	160	0.01
KL26-04	391.4	394.4	1.93	19300	1.19	13.3	269	16	32	22	5	46	0.3	13.2	58	0.01
KL26-04	394.4	397.4	1.99	19900	1.63	21	186	16	36	269	4	107	0.4	12.3	165	0.01
KL26-04	397.4	400.4	1.54	15400	0.55	20.1	138	18	37	86	8	56	0.4	20.5	67	0.01
KL26-04	400.4	401.9	1.53	15300	2.07	22.6	175	21	57	91	6	35	0.2	16.0	121	0.01
KL26-04	401.9	406.6	1.41	14100	1.8	19.5	273	66	61	69	11	46	0.5	28.5	78	0.01
KL26-04	406.6	408	1.28	12800	0.77	16.2	16600	326	22	15	74	13	0.01	86.5	63	0.12
KL26-04	408	410.5	0.025	250	0.17	2.7	1640	560	62	6	7	1	1.2	2.5	30	0.01
KL26-04	410.5	413.6	0.056	560	0.13	2.8	1520	550	40	8	4	4	1.2	2.5	44	0.01
KL26-04	413.6	416.6	0.106	1060	0.04	1	470	194	15	21	5	1	1.9	0.0	28	0.01
KL26-04	416.6	419.7	0.0207	207	0.03	0.1	108	65	16	9	0.01	1	1.5	0.0	21	0.01
KL26-04	419.7	422.8	0.007	70	0.02	0.1	122	93	24	9	1	4	0.9	1.9	31	0.01
KL26-04	422.8	425.8	0.0103	103	0.02	0.1	380	44	18	6	1	1	1.5	1.6	24	0.01
KL26-04	425.8	429.5	0.046	460	0.09	0.9	257	48	32	10	19	5	2.4	4.0	48	0.01
KL26-04	429.5	432.6	0.164	1640	0.33	10.7	188	68	42	198	107	6	0.6	7.3	76	0.01
KL26-04	432.6	435.7	0.0095	95	0.28	1.1	43	18	33	309	7	1	0.4	0.0	37	0.01
KL26-04	435.7	439.1	0.0205	205	0.04	1	27	14	14	1080	3	5	0.6	1.5	47	0.01
KL26-04	439.1	443.8	0.0206	206	0.01	0.1	27	27	4	582	2	3	0.9	0.0	183	0.01
KL26-04	443.8	446.8	0.0113	113	0.01	0.1	30	13	3	231	2	4	0.6	0.0	72	0.01
KL26-04	446.8	449.8	0.0261	261	0.05	1.9	34	27	9	2570	7	6	0.6	3.8	176	0.01
KL26-04	449.8	452.8	0.12	1200	0.29	18	24900	12000	75	197	141	6	11.9	13.2	65	0.01
KL26-04	452.8	454.6	0.0306	306	0.19	2.1	233	219	25	260	68	5	1.3	2.8	35	0.01
KL26-04	454.6	456.9	1.06	10600	2.07	22.5	5200	233	240	273	820	168	1.8	39.0	123	0.01
KL26-04	456.9	458.8	0.09	900	0.44	8.8	8100	3800	62	620	195	8	2.5	10.2	41	0.01
KL26-04	458.8	461.8	0.069	690	0.05	1.5	422	600	18	18	4	1	2.6	2.8	39	0.01
KL26-04	461.8	464.8	0.0133	133	0.04	3.9	2700	3000	13	13	8	1	3.5	8.3	51	0.01
KL26-04	464.8	467.8	0.041	410	0.03	1.4	230	470	13	18	3	2	2.5	2.5	32	0.01
KL26-04	467.8	470.8	0.17	1700	0.05	1.5	199	403	17	15	2	1	6.7	1.8	27	0.01
KL26-04	470.8	473.8	0.0067	67	0.05	1.3	175	409	17	8	4	1	1.5	0.0	23	0.01
KL26-04	473.8	476.8	0.0275	275	0.17	2.4	1640	930	34	10	5	1	2.2	5.0	31	0.1
KL26-04	476.8	479.8	0.0171	171	0.2	2.7	1910	1270	36	17	7	1	2.5	6.3	32	0.01
KL26-04	479.8	482.4	0.0247	247	0.18	6.3	1970	1870	38	13	14	1	3.2	6.0	25	0.01
KL26-04	482.4	485.4	0.007	70	0.04	0.1	158	118	14	8	1	1	1.1	3.2	26	0.01
KL26-05	0	3	0.0067	67	0.06	1.4	420	610	10	11	0.01	1	1.9	19.5	22	0.01
KL26-05	3	6	0.0055	55	0.02	0.1	78	59	7	3	3	1	0.7	2.7	24	0.01
KL26-05	6	9	0.0134	134	0.09	0.5	280	83	30	12	9	1	1.4	3.1	21	0.01
KL26-05	9	12	0.028	280	0.25	2.6	620	570	40	21	6	1	3.3	4.0	24	0.01
KL26-05	12	15	0.0158	158	0.02	0.1	55	40	4	5	0.01	1	1.1	3.0	26	0.01
KL26-05	15	18	0.17	1700	0.02	0.1	102	189	2	16	1	1	5.7	3.0	26	0.01
KL26-05	18	21	0.033	330	0.02	0.1	68	67	1	10	0.01	1	2.1	3.2	17	0.01
KL26-05	21	24	0.056	560	0.05	0.1	129	49	7	11	17	1	1.3	3.5	35	0.01
KL26-05	24	27	0.0038	38	0.02	0.1	70	27	4	3	0.01	1	0.3	1.7	42	0.01
KL26-05	27	30	0.0049	49	0.01	0.1	79	28	8	3	0.01	1	0.4	1.2	25	0.01
KL26-05	30	33	0.0042	42	0.02	0.1	60	23	7	4	0.01	2	0.5	1.2	38	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL26-05	33	36	0.0217		217	0.23	1.9	1540	730	33	9	4	1	1.9	4.7	22	0.01
KL26-05	36	38.3	0.0069		69	0.02	0.1	60	27	5	3	0.01	1	0.5	1.2	34	0.01
KL26-05	38.3	41.3	0.0175		175	0.01	0.1	92	40	10	4	0.01	1	0.8	2.0	56	0.01
KL26-05	41.3	45	0.0289		289	0.06	18.9	13900	4500	30	7	26	3	8.8	25.5	62	0.13
KL26-05	45	50.5	0.0115		115	0.06	2.4	620	810	6	13	0.01	2	1.6	23.1	24	0.01
KL26-05	50.5	53.5	0.052		520	0.3	150	10500	58400	52	16	200	1	39	2550.0	263	0.01
KL26-05	53.5	57	0.048		480	0.1	11.7	245	3140	18	4	7	2	3.7	25.0	31	0.01
KL26-05	57	60	0.0108		108	0.06	12.4	1710	4820	90	15	7	1	11.1	14.3	21	0.01
KL26-05	60	63	0.0071		71	0.01	1.2	175	420	15	10	0.01	1	4.1	1.0	24	0.01
KL26-05	63	66	0.0297		297	0.1	1.4	195	530	23	11	1	2	3	0.0	31	0.01
KL26-05	66	69	0.0144		144	0.13	1	174	61	26	4	0.01	1	2.2	0.0	27	0.01
KL26-05	69	72	0.0156		156	0.01	0.7	259	132	1	5	0.01	2	0.3	0.0	82	0.01
KL26-05	72	75	0.0078		78	0.01	2.1	223	440	13	12	0.01	1	2.4	0.0	20	0.01
KL26-05	75	78	0.008		80	0.01	1.2	103	287	10	6	0.01	1	1.7	1.1	22	0.01
KL26-05	78	81	0.0081		81	0.01	0.1	44	42	2	7	0.01	1	0.5	0.5	24	0.01
KL26-05	81	84	0.0084		84	0.02	6.2	960	800	9	5	0.01	1	2.1	1.5	27	0.01
KL26-05	84	87	0.0065		65	0.01	0.1	186	164	1	6	0.01	2	0.5	1.0	19	0.01
KL26-05	87	90	0.0064		64	0.01	0.1	76	30	4	8	0.01	1	0.4	1.0	21	0.01
KL26-05	90	93	0.0039		39	0.01	0.1	91	29	3	7	0.01	1	0.4	0.7	19	0.01
KL26-05	93	96	0.006		60	0.01	0.1	68	26	5	13	0.01	1	0.3	0.7	21	0.01
KL26-05	96	99	0.0048		48	0.01	0.1	27	20	4	7	0.01	1	0.4	0.0	15	0.01
KL26-05	99	102	0.0039		39	0.01	0.1	39	13	4	7	0.01	1	0.2	0.0	12	0.01
KL26-05	102	105	0.0074		74	0.01	0.1	33	10	1	4	0.01	1	0.01	0.5	17	0.01
KL26-05	105	108	0.0025		25	0.01	0.1	21	11	2	6	0.01	1	0.01	0.0	15	0.01
KL26-05	108	111	0.0032		32	0.01	0.1	29	23	2	4	0.01	1	0.2	0.5	36	0.01
KL26-05	111	114	0.0041		41	0.01	0.1	38	95	1	4	0.01	1	0.8	0.0	68	0.01
KL26-05	114	119.8	0.0059		59	0.26	5.5	182	820	38	7	0.01	1	3.5	4.3	37	0.01
KL26-05	119.8	121.5	0.0066		66	0.13	6	1820	3810	13	6	0.01	1	4.1	5.1	23	0.01
KL26-05	121.5	123	0.0068		68	0.19	5.6	437	3050	13	7	0.01	1	4.2	3.0	21	0.01
KL26-05	123	126	0.0083		83	0.07	4.4	590	1780	14	9	1	1	3.4	2.3	27	0.01
KL26-05	126	129	0.0097		97	0.03	0.8	103	249	7	4	0.01	1	1.2	1.5	23	0.01
KL26-05	129	132	0.0035		35	0.04	1.5	56	298	12	2	0.01	1	0.9	3.0	21	0.01
KL26-05	132	135	0.0083		83	0.05	2.4	33	164	7	4	1	1	1.5	1.5	16	0.01
KL26-05	135	138	0.0109		109	0.03	8.8	480	3440	47	4	5	1	5.5	6.8	27	0.01
KL26-05	138	141	0.0044		44	0.02	1.3	28	252	6	2	1	1	0.6	2.3	13	0.01
KL26-05	141	142.9	0.0029		29	0.01	2.6	24	181	5	3	4	1	0.5	1.0	26	0.01
KL26-05	142.9	145.7	0.0059		59	0.01	1.8	27	201	4	1	3	1	0.8	1.0	29	0.01
KL26-05	145.7	159	0.0076		76	0.01	7.4	530	1190	9	1	6	1	1.6	1.8	28	0.01
KL26-05	159	167.5	0.013		130	0.04	23.3	110	3640	45	1	0.01	1	9.3	3.2	27	0.01
KL26-05	167.5	179.8	0.0027		27	0.03	2.5	225	1110	7	4	0.01	1	1.6	1.5	21	0.01
KL26-05	179.8	183	0.0028		28	0.04	3.7	1290	610	9	2	0.01	1	1.7	2.0	11	0.01
KL26-05	183	189	0.0044		44	0.11	16	3500	7300	10	8	0.01	1	15	2.8	19	0.01
KL26-05	189	193.5	0.0029		29	0.06	2.1	850	810	11	6	0.01	1	1.7	2.8	19	0.14
KL26-05	193.5	198	0.0018		18	0.05	2	560	990	10	13	0.01	1	3.1	1.5	13	0.01
KL26-05	198	207	0.0014		14	0.06	3.1	500	2650	9	7	0.01	1	3	2.3	9	0.01
KL26-05	207	210	0.058		580	0.03	79	7200	5700	110	11	0.01	1	285	9.0	23	0.19
KL26-05	210	211.7	0.0037		37	0.04	4.2	630	1510	14	60	0.01	1	3.3	3.5	9	0.01
KL26-05	211.7	214.2	0.0022		22	0.05	3.1	156	1190	9	39	3	1	2.1	3.0	11	0.01
KL26-05	214.2	217.7	0.0031		31	0.1	4.3	128	500	13	15	1	1	3.2	4.7	19	0.01
KL26-05	217.7	219.6	0.0013		13	0.03	1	67	68	5	12	0.01	1	1	1.5	20	0.01
KL26-05	219.6	222	0.002		20	0.05	1.8	391	260	10	15	1	1	1.2	3.0	20	0.01
KL26-05	222	225	0.0083		83	0.04	1.9	232	398	8	21	2	1	0.9	3.5	16	0.01
KL26-05	225	228	0.0043		43	0.04	1.4	233	196	9	10	0.01	1	1.5	2.0	20	0.01
KL26-05	228	231	0.0051		51	0.17	8.2	470	510	13	11	0.01	1	4.5	5.5	20	0.12
KL26-05	231	234	0.0101		101	0.04	2.1	460	215	14	12	0.01	1	3.3	4.8	24	0.01
KL26-05	234	237	0.0079		79	0.07	4.2	263	214	13	13	0.01	1	1.7	4.0	13	0.12
KL26-05	237	240	0.0108		108	0.27	51	5020	4590	20	14	2	1	6.5	7.8	16	1.34
KL26-05	240	243.2	0.0119		119	0.11	3.8	1300	860	19	18	2	1	1.5	8.3	13	0.42
KL26-05	243.2	246	0.171		1710	0.42	10.1	2530	810	180	126	10	5	10.8	12.5	35	2.57
KL26-05	246	249	0.044		440	0.19	8.9	3600	3610	75	48	7	1	5.9	12.5	27	2.12
KL26-05	249	252	0.014		140	0.06	3.2	1130	820	18	49	4	1	1.3	4.8	18	0.28
KL26-05	252	255	0.0075		75	0.09	3.4	1480	1390	19	44	6	1	1.5	5.0	17	0.21
KL26-05	255	258	0.0092		92	0.07	4.2	750	1360	8	48	8	1	0.6	5.0	15	0.16

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL26-05	258	276	0.165	1650	0.19	9.1	2880	1140	45	154	45	37	1.1	16.5	35	0.23
KL26-05	276	279.5	0.326	3260	0.76	23.4	5290	2730	180	41	52	13	5.8	14.8	50	1.28
KL26-05	279.5	282.1	1.26	12600	1.31	26.6	1010	570	260	2930	171	48	6.2	32.0	195	0.25
KL26-05	282.1	284.5	0.437	4370	1.49	18.6	200	151	300	7800	121	60	6.1	37.8	69	0.1
KL26-05	284.5	287.5	1.12	11200	2.41	33	4000	367	240	3750	160	100	5.8	56.5	144	0.14
KL26-05	287.5	290.7	0.92	9200	1.4	18.8	4800	124	180	1810	79	58	7.4	48.3	148	0.25
KL26-05	290.7	293	1.54	15400	1.73	40	39900	350	140	327	120	78	7.1	42.5	176	2.2
KL26-05	293	296	1.48	14800	1.75	33	2500	334	330	920	620	170	7.8	95.8	263	0.18
KL26-05	296	299.1	1.73	17300	1.71	30.1	900	104	260	41	85	90	6.6	60.5	174	0.11
KL26-05	299.1	301.9	1.37	13700	1.43	26.4	7500	700	300	70	65	80	7.3	60.5	151	0.27
KL26-05	301.9	303.8	1.16	11600	0.92	22.3	3400	440	160	86	70	67	5	41.5	149	0.18
KL26-05	303.8	306	1.39	13900	0.68	22.4	510	410	130	69	64	66	5.1	37.5	189	0.01
KL26-05	306	309	1.2	12000	0.81	25.6	1190	680	210	85	79	60	5	46.2	168	0.01
KL26-05	309	312	0.99	9900	0.64	17.7	780	154	130	48	93	31	4.5	69.5	169	0.1
KL26-05	312	315	1.04	10400	1.16	31.1	1810	530	240	38	148	73	6.8	64.5	194	0.2
KL26-05	315	318	1.27	12700	0.93	23.4	1130	114	180	370	80	48	5.5	30.2	153	0.18
KL26-05	318	320.5	1.05	10500	1.6	20.7	520	214	200	630	31	19	5.2	26.3	175	0.19
KL26-05	320.5	323.2	1.38	13800	0.88	27.9	3600	358	280	302	19	27	3.7	22.2	133	0.18
KL26-05	323.2	325.2	1	10000	0.81	70	52800	5700	130	180	150	27	2.5	50.5	137	0.35
KL26-05	325.2	327	1.03	10300	1.09	113	358000	8500	300	94	382	28	5	117.0	85	2.2
KL26-05	327	330	1.04	10400	1.17	184	267000	44000	300	25	398	49	5.8	172.0	185	1.6
KL26-05	330	332	1.3	13000	1.31	30	32300	2400	200	1100	130	74	3.4	98.0	228	0.3
KL26-05	332	333.7	1.18	11800	1.57	53.5	30000	27700	580	82	98	66	23	92.5	186	0.2
KL26-05	333.7	336	0.092	920	0.5	10.8	7200	2900	120	142	17	5	6.1	16.5	50	0.01
KL26-05	336	342	0.0185	185	0.08	3.5	2870	1410	38	74	6	1	2.5	5.5	19	0.01
KL26-05	342	345	0.41	4100	0.52	17.2	25800	8300	150	56	60	17	9.8	30.2	31	0.31
KL26-05	345	348	0.122	1220	0.23	18.4	7700	7000	55	174	63	4	5.3	18.7	33	0.01
KL26-05	348	350.7	0.101	1010	1.77	4	880	1170	240	96	6	5	2.1	9.3	48	0.01
KL26-05	350.7	354	0.072	720	0.38	3.2	1490	680	190	44	3	5	16.9	6.2	20	0.01
KL26-05	354	357	0.072	720	0.13	5.1	4930	1560	210	22	7	2	15	10.5	21	0.01
KL26-05	357	360	0.0102	102	0.03	0.5	860	143	12	11	1	2	0.5	3.7	18	0.12
KL26-05	360	363	0.0231	231	0.19	5.2	1410	1750	34	36	6	1	3.4	9.0	23	0.12
KL26-05	363	366	0.0147	147	0.15	3.3	1030	760	14	19	5	1	1.2	5.5	21	0.01
KL26-05	366	368	0.014	140	0.04	1.7	640	289	26	20	4	1	2.2	3.0	14	0.01
KL26-05	368	369.4	0.0296	296	0.04	4.1	690	720	54	38	7	1	4.6	6.0	16	0.01
KL26-05	369.4	372	0.0166	166	0.05	3.8	870	610	28	17	7	1	1.9	6.2	17	0.01
KL26-05	381	384	0.0082	82	0.04	1.1	540	218	10	22	5	1	0.4	3.0	13	0.01
KL26-05	384	387.1	0.0091	91	0.04	2.2	570	188	23	70	5	3	1.5	4.7	18	0.01
KL26-05	387.1	390.1	0.0301	301	0.23	5.2	177	860	66	51	16	2	2.9	7.0	15	0.01
KL26-05	390.1	392.4	0.0189	189	0.35	3.6	800	850	34	57	9	4	1.4	8.0	20	0.01
KL26-05	392.4	394.4	0.0347	347	0.17	4.7	1970	710	58	66	29	3	3.6	14.2	12	0.01
KL26-05	394.4	396	0.0183	183	0.18	5.4	1410	670	20	33	14	2	1.3	7.3	14	0.01
KL26-05	396	398.5	0.0192	192	0.48	6.7	1850	950	20	40	18	2	1.7	10.7	11	0.01
KL26-05	398.5	401.6	0.0171	171	0.27	5.1	1020	750	18	40	13	2	1.3	9.0	13	0.01
KL26-05	401.6	404.4	0.0166	166	0.32	4.2	1120	930	31	39	9	3	2.5	6.0	16	0.01
KL26-05	404.4	407.5	0.151	1510	0.2	11.5	1350	1170	300	300	28	6	18.9	13.7	27	0.01
KL26-05	407.5	409.7	0.049	490	0.59	22.4	3600	3300	240	325	39	12	5.8	49.0	78	0.18
KL26-05	409.7	411.7	0.119	1190	0.13	22.7	13100	6000	430	400	22	6	23	25.5	69	0.2
KL26-05	411.7	417	0.021	210	0.21	1	550	410	9	6	2	1	1.2	3.5	9	0.01
KL26-05	417	420	0.0138	138	0.1	2	383	320	10	17	2	1	1.1	6.6	10	0.01
KL26-05	420	422.2	0.0049	49	0.22	0.1	343	179	10	4	0.01	1	0.6	3.0	11	0.01
KL26-05	422.2	425.2	0.008	80	0.1	0.1	172	187	10	3	2	1	0.5	1.7	6	0.01
KL26-05	425.2	428.3	0.0041	41	0.1	0.6	187	150	7	1	0.01	1	0.4	1.1	12	0.01
KL26-05	428.3	431.4	0.0038	38	0.12	1	470	324	15	3	0.01	1	0.6	0.8	15	0.01
KL26-05	431.4	434	0.0078	78	0.21	0.7	228	127	9	5	0.01	1	0.5	0.5	10	0.01
KL26-05	434	436.3	0.0098	98	0.19	1.4	450	303	11	3	0.01	1	1.9	1.0	15	0.01
KL26-06	0	2.6	0.0035	35	0.02	0.9	164	145	23	2	1	1	2.1	2.7	22	0.01
KL26-06	2.6	4.4	0.0045	45	0.04	0.6	116	129	19	2	0.01	1	1.5	1.4	21	0.01
KL26-06	4.4	7.4	0.0049	49	0.02	1.5	225	600	28	2	2	1	2.8	2.7	18	0.01
KL26-06	7.4	10.4	0.0346	346	0.13	21.5	3190	6200	140	26	29	2	31.3	17.9	29	0.01
KL26-06	10.4	13.4	0.006	60	0.07	0.9	200	206	21	2	0.01	1	1.7	1.8	30	0.01
KL26-06	13.4	16.4	0.0039	39	0.04	0.9	268	194	29	3	0.01	1	1.1	2.0	29	0.01
KL26-06	16.4	19.4	0.0023	23	0.03	0.1	103	38	15	2	0.01	1	1	1.3	19	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL26-06	19.4	22.4	0.0032		32	0.03	0.1	125	56	13	2	0.01	1	1.1	1.0	17	0.01
KL26-06	22.4	25.4	0.002		20	0.05	0.1	51	35	9	1	0.01	1	0.8	1.1	23	0.01
KL26-06	25.4	28.4	0.0033		33	0.01	0.1	66	34	11	1	0.01	1	0.7	0.7	23	0.01
KL26-06	28.4	31.4	0.0065		65	0.02	0.1	108	38	19	1	0.01	1	1.1	2.8	34	0.01
KL26-06	31.4	34.4	0.0034		34	0.01	0.1	90	47	14	1	0.01	1	0.3	0.8	27	0.01
KL26-06	34.4	37.4	0.0033		33	0.01	0.1	126	46	10	1	0.01	1	0.3	0.8	31	0.01
KL26-06	37.4	40.4	0.0029		29	0.01	0.1	120	32	14	1	0.01	1	0.6	1.1	32	0.01
KL26-06	40.4	43.4	0.0047		47	0.01	0.1	171	87	28	1	0.01	2	0.9	4.7	42	0.01
KL26-06	43.4	45.8	0.0033		33	0.01	0.1	93	134	21	1	0.01	1	0.7	1.3	33	0.01
KL26-06	45.8	48.4	0.018		180	0.01	0.7	74	160	49	3	0.01	7	1.8	1.6	93	0.01
KL26-06	48.4	52	0.0376		376	0.49	19.3	9300	8700	150	10	6	1	30	6.3	33	0.15
KL26-06	52	55	0.0356		356	2.26	72	4400	14000	100	14	134	3	33	86.5	88	0.26
KL26-06	55	57.9	0.0171		171	0.71	14.6	1560	7000	84	25	13	1	12.8	4.3	96	0.13
KL26-06	57.9	59.9	0.0385		385	0.35	12.3	205	1420	69	7	53	1	9.8	8.1	59	0.01
KL26-06	59.9	63.1	0.0147		147	0.32	5.4	910	1030	34	10	9	1	6.4	2.8	37	0.13
KL26-06	63.1	65.1	0.0053		53	0.29	2.5	730	740	27	7	4	1	4	1.9	225	0.01
KL26-06	65.1	68.9	0.0038		38	0.17	2	189	178	29	6	3	1	6.4	2.2	222	0.01
KL26-06	68.9	71.8	0.0019		19	0.05	0.8	92	107	9	6	1	1	2.4	1.0	172	0.01
KL26-06	71.8	74.6	0.14		1400	0.02	0.1	225	118	13	14	0.01	3	0.2	0.0	15	0.01
KL26-06	74.6	77.9	0.0064		64	0.03	1	193	190	5	12	2	1	3.3	1.6	126	0.01
KL26-06	77.9	81.3	0.0038		38	0.13	1.5	251	138	22	8	1	1	3.2	0.7	118	0.01
KL26-06	81.3	84.4	0.0039		39	0.23	1.9	154	48	25	6	1	1	3.9	1.2	136	0.01
KL26-06	84.4	86.3	0.004		40	0.93	2.8	179	70	25	10	2	1	9.4	1.9	151	0.01
KL26-06	86.3	88.4	0.0035		35	0.01	1.6	114	56	15	5	7	1	2.2	0.9	48	0.01
KL26-06	88.4	91	0.005		50	0.16	14.6	200	1010	17	9	27	1	3.6	2.9	28	0.01
KL26-06	91	93.6	0.003		30	0.28	2	210	175	29	11	1	1	4.4	1.6	18	0.01
KL26-06	93.6	95.9	0.0021		21	0.17	1.3	129	318	26	8	0.01	1	3	1.3	14	0.01
KL26-06	95.9	97.4	0.001		10	0.12	1.1	294	1160	38	5	0.01	1	2.2	1.6	15	0.01
KL26-06	97.4	100.4	0.0022		22	0.03	0.9	271	379	30	5	0.01	1	1.4	0.0	13	0.01
KL26-06	100.4	115.4	0.064		640	0.35	40	24700	48000	95	5	7	1	45	22.6	26	0.12
KL26-06	115.4	117	0.0013		13	0.01	0.7	250	384	0.01	4	0.01	1	0.8	0.5	17	0.01
KL26-06	117	120.4	0.0006		6	0.02	0.6	199	298	3	3	0.01	1	0.4	0.6	17	0.01
KL26-06	120.4	122.9	0.0015		15	0.01	1.2	420	680	0.01	2	0.01	1	1	0.8	16	0.01
KL26-06	122.9	125.9	0.0022		22	0.01	2.1	1630	1340	4	3	0.01	1	1.3	0.5	14	0.01
KL26-06	125.9	128.6	0.0066		66	0.03	4.2	1500	2500	19	10	0.01	1	3.5	2.5	21	0.01
KL26-06	128.6	129.8	0.0038		38	0.01	0.6	216	280	2	2	0.01	1	0.5	0.0	21	0.01
KL26-06	129.8	132.3	0.0022		22	0.01	1.2	710	830	2	2	0.01	1	0.8	1.3	16	0.01
KL26-06	132.3	134.9	0.0016		16	0.01	1.3	520	780	1	3	0.01	1	1.1	1.2	21	0.01
KL26-06	134.9	137.9	0.0021		21	0.01	0.7	267	376	1	5	0.01	1	0.8	1.1	22	0.01
KL26-06	137.9	139.4	0.0021		21	0.01	1	227	990	0.01	1	0.01	1	1.5	1.2	24	0.01
KL26-06	139.4	141.9	0.0019		19	0.01	0.9	386	580	0.01	1	0.01	1	0.8	0.9	21	0.01
KL26-06	141.9	144.6	0.0015		15	0.01	0.1	288	371	0.01	1	0.01	1	0.5	0.5	20	0.01
KL26-06	144.6	147	0.0016		16	0.01	0.6	122	188	1	1	0.01	1	0.6	0.8	21	0.01
KL26-06	147	150	0.0013		13	0.01	0.1	54	83	1	4	0.01	3	0.2	0.0	20	0.01
KL26-06	150	152.4	0.0014		14	0.03	0.1	93	158	1	4	0.01	1	0.4	0.7	22	0.01
KL26-06	152.4	154.9	0.0014		14	0.01	0.7	228	395	22	4	0.01	1	0.7	0.0	19	0.01
KL26-06	154.9	157.3	0.0013		13	0.01	0.8	540	560	8	3	0.01	1	1.8	1.1	23	0.01
KL26-06	157.3	160.4	0.0027		27	0.01	1.7	600	1700	3	3	0.01	1	1.7	1.1	24	0.01
KL26-06	160.4	163.9	0.0009		9	0.01	0.1	116	221	1	4	0.01	1	0.4	0.5	22	0.01
KL26-06	163.9	166.4	0.0014		14	0.01	0.9	335	550	3	5	0.01	2	0.9	0.9	20	0.01
KL26-06	166.4	169.3	0.0014		14	0.01	1.8	387	530	5	10	0.01	1	1.4	1.1	11	0.01
KL26-06	169.3	172.4	0.0011		11	0.01	1	263	223	3	11	0.01	1	0.9	0.8	10	0.01
KL26-06	172.4	175.6	0.0013		13	0.01	1	372	490	2	6	0.01	1	1.1	0.8	10	0.01
KL26-06	175.6	178.4	0.0011		11	0.01	1.2	325	420	3	12	0.01	1	1.2	0.7	8	0.01
KL26-06	178.4	180	0.0009		9	0.01	0.6	197	282	2	7	0.01	1	0.6	0.7	11	0.01
KL26-06	180	182.6	0.0006		6	0.01	0.1	219	278	1	4	0.01	1	0.6	1.3	10	0.01
KL26-06	182.6	185.7	0.0012		12	0.01	0.6	165	242	1	6	0.01	1	2.3	1.0	12	0.01
KL26-06	185.7	188.5	0.0011		11	0.01	0.1	163	233	0.01	3	0.01	1	0.5	0.0	12	0.01
KL26-06	188.5	190.9	0.0012		12	0.01	2	1790	710	2	5	0.01	1	1.9	1.1	10	0.01
KL26-06	190.9	194	0.0015		15	0.01	0.6	235	246	0.01	5	0.01	1	0.5	0.5	7	0.01
KL26-06	194	196.1	0.0018		18	0.01	1	384	670	6	14	0.01	1	1	1.7	11	0.01
KL26-06	196.1	198.8	0.0219		219	0.03	1	266	480	20	10	0.01	1	1.3	2.3	18	0.01
KL26-06	198.8	201.6	0.0034		34	0.01	1.2	277	740	4	5	0.01	3	1.7	1.5	17	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL26-08	229.5	232														
KL26-08	232	234.8														
KL26-08	234.8	237.7														
KL26-08	237.7	240														
KL26-08	240	243														
KL26-08	243	246														
KL26-08	246	249														
KL26-08	249	250.5														
KL26-08	250.5	253.5														
KL26-08	253.5	256.5	0.0114	114	0.02	6.3	4900	4590	15	7	4	1	7.8	11.9	25	0.01
KL26-08	256.5	259.5	0.063	630	0.14	15.9	15300	12400	29	14	16	1	14	57.5	34	0.01
KL26-08	259.5	262.5	0.0083	83	0.07	4.7	1720	1740	31	80	13	2	3	23.8	31	0.01
KL26-08	262.5	265.5	0.04	400	0.09	3.5	1070	1340	38	189	28	1	0.8	6.5	80	0.01
KL26-08	265.5	268.5	0.0089	89	0.04	1.4	470	330	28	636	8	1	0.6	6.0	52	0.01
KL26-08	268.5	271.5	0.55	5500	0.47	13.2	146000	1590	22	142	340	104	1	191.0	31	0.01
KL26-08	271.5	274.5	0.61	6100	0.53	29.2	68000	3800	39	19	1760	45	2.7	136.0	22	0.01
KL26-08	274.5	277.5	0.187	1870	0.54	13.1	40600	770	24	47	370	26	1.1	137.0	26	0.01
KL26-08	277.5	280.5	0.127	1270	0.34	2.3	3300	307	48	309	100	4	6.1	33.8	54	0.01
KL26-08	280.5	282	0.27	2700	0.32	8.7	26200	720	24	66	860	31	2	181.0	21	0.01
KL26-08	282	283.8	1.17	11700	3.17	14.8	79000	700	24	80	16	99	1.4	78.5	34	0.01
KL26-08	283.8	286.1	0.52	5200	2.24	4.8	12200	124	21	68	33	45	1.4	30.3	38	0.01
KL26-08	286.1	287.8	0.145	1450	0.57	1.8	3300	59	18	85	50	7	1	21.8	21	0.01
KL26-08	287.8	290.8	0.37	3700	0.95	5.6	7200	100	11	600	71	14	1	28.8	26	0.01
KL26-08	290.8	293.8	1.18	11800	2.08	12.3	24600	51	25	425	26	67	0.4	45.0	31	0.01
KL26-08	293.8	296.8	0.51	5100	1.85	4.3	21000	27	18	171	63	48	0.6	26.0	24	0.01
KL26-08	296.8	299.8	0.118	1180	0.22	0.8	162	42	18	2060	5	3	0.3	7.3	33	0.01
KL26-08	299.8	302.8	1.04	10400	2.5	32.5	35500	4400	27	857	114	63	1.2	46.3	86	0.01
KL26-08	302.8	305.8	0.63	6300	0.84	8.1	7200	141	14	35	21	95	0.7	23.0	39	0.01
KL26-08	305.8	308.8	0.91	9100	1.44	7.7	1200	25	4	17	7	84	0.4	12.6	26	0.01
KL26-08	308.8	309.6	1.04	10400	1.02	6.9	440	55	5	6	8	165	0.3	14.0	27	0.01
KL26-08	309.6	311.8	0.24	2400	0.58	1.3	336	42	13	50	9	37	1	30.5	67	0.01
KL26-08	311.8	314.8	0.181	1810	0.37	2.7	14600	15	12	23	3	17	0.7	23.5	32	0.01
KL26-08	314.8	317.3	0.38	3800	0.5	3.8	20600	33	9	20	2	24	0.9	10.8	24	0.01
KL26-08	317.3	319.1	0.51	5100	0.63	3	490	71	8	394	2	65	0.5	30.5	34	0.01
KL26-08	319.1	320.8	0.52	5200	1.44	3.1	440	72	27	153	9	110	1.9	62.0	65	0.01
KL26-08	320.8	323.8	4.24	42400	4.42	35.4	10200	520	180	329	55	132	2.9	21.5	65	0.01
KL26-08	323.8	326.8	0.492	4920	0.58	1.4	174	28	10	196	7	38	0.6	22.5	28	0.01
KL26-08	326.8	329.8	0.92	9200	0.5	1.9	167	17	2	41	3	127	0.4	51.8	32	0.01
KL26-08	329.8	332.8	0.87	8700	1	3.8	141	21	5	73	6	91	0.3	24.2	63	0.01
KL26-08	332.8	335.8	1.04	10400	1.48	3.8	119	18	6	30	6	70	0.6	26.8	45	0.01
KL26-08	335.8	338.8	1.27	12700	1.25	4.1	130	17	2	74	2	94	0.4	22.0	60	0.01
KL26-08	338.8	341.8	3.14	31400	1.84	6.7	214	14	2	172	1	124	0.3	25.0	43	0.01
KL26-08	341.8	343.8	4.34	43400	2.72	6.2	282	30	1	890	1	123	0.2	25.0	46	0.01
KL26-08	343.8	346.8	0.93	9300	0.42	1.7	140	16	3	106	0.01	32	0.3	9.0	39	0.01
KL26-08	346.8	348.5	1.29	12900	0.54	3.2	116	9	4	172	0.01	34	0.3	10.5	62	0.01
KL26-08	348.5	351.5	0.82	8200	0.35	1.8	91	14	3	302	0.01	18	0.4	9.3	45	0.01
KL26-08	351.5	353.8	0.342	3420	0.15	1	82	14	4	120	0.01	5	0.3	18.5	87	0.01
KL26-08	353.8	355.7	1.2	12000	0.43	3.9	120	12	2	2930	0.01	19	0.2	12.0	69	0.01
KL26-08	355.7	357.6	0.449	4490	0.22	1	86	9	3	920	0.01	8	0.3	5.0	68	0.01
KL26-08	357.6	359.2	0.72	7200	0.3	1.9	94	15	3	830	0.01	15	0.3	9.8	87	0.01
KL26-08	359.2	360.7	1.37	13700	0.79	4.2	218	34	21	3020	1	20	5	11.0	78	0.01
KL26-08	360.7	362.8	0.8	8000	0.55	1.8	59	20	13	391	0.01	13	0.01	5.5	81	0.01
KL26-08	362.8	365.8	0.9	9000	0.74	2.3	70	21	3	164	1	12	0.01	7.3	67	0.01
KL26-08	365.8	368.8	1.05	10500	1.1	1.9	140	35	1	49	0.01	11	0.01	9.0	84	0.01
KL26-08	368.8	371.8	1.11	11100	0.48	1.7	122	28	0.01	96	0.01	17	0.01	5.0	83	0.01
KL26-08	371.8	374.8	0.51	5100	0.32	1.4	175	16	5	80	0.01	14	0.01	4.8	138	0.01
KL26-08	374.8	377.8	0.65	6500	0.37	1.3	73	10	1	81	0.01	13	0.01	7.3	124	0.01
KL26-08	377.8	380.8	0.8	8000	0.41	1.6	80	18	0.01	49	0.01	12	0.01	6.3	108	0.01
KL26-08	380.8	383.8	1.29	12900	0.91	2.2	78	29	1	134	0.01	11	0.01	6.0	75	0.01
KL26-08	383.8	386.8	1.34	13400	0.5	4.2	1620	670	5	102	3	14	0.4	10.0	62	0.01
KL26-08	386.8	389.8	1.44	14400	1.29	2.5	384	20	0.01	168	1	11	0.01	9.5	111	0.01
KL26-08	389.8	392.8	0.83	8300	0.93	1.7	84	35	0.01	110	0.01	11	0.01	6.5	107	0.01
KL26-08	392.8	395.8	0.96	9600	0.87	1.7	65	15	0.01	159	1	10	0.01	5.6	75	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL26-08	395.8	398.8	0.78	7800	0.47	1.4	72	32	1	91	0.01	8	0.01	5.5	65	0.01
KL26-08	398.8	401.8	0.68	6800	0.67	1.4	69	28	2	57	0.01	8	0.5	5.0	74	0.01
KL26-08	401.8	404.8	0.72	7200	0.47	1.4	52	19	0.01	85	0.01	8	0.01	4.0	76	0.01
KL26-08	404.8	407.8	1.24	12400	0.51	2.3	87	18	0.01	280	0.01	10	0.01	4.5	67	0.01
KL26-08	407.8	410.8	0.68	6800	0.42	1.5	56	16	0.01	55	0.01	9	0.01	2.8	75	0.01
KL26-08	410.8	413.8	0.66	6600	0.48	1.3	71	27	1	30	0.01	10	0.01	5.3	110	0.01
KL26-08	413.8	416.8	0.91	9100	0.65	1.4	68	21	1	34	0.01	13	0.01	4.3	72	0.01
KL26-08	416.8	419.8	0.66	6600	0.58	1.5	61	15	1	44	0.01	8	0.01	5.3	132	0.01
KL26-08	419.8	422.8	0.68	6800	0.46	1.7	81	52	7	30	0.01	10	0.9	6.0	79	0.01
KL26-08	422.8	425.8	0.85	8500	0.6	2.3	90	23	2	60	0.01	16	0.01	5.8	75	0.01
KL26-08	425.8	428.8	1.2	12000	2.95	6.3	103	104	130	40	14	21	33	18.5	22	0.01
KL26-08	428.8	431.8	1.32	13200	0.62	1.7	49	14	1	69	0.01	15	0.3	10.5	34	0.01
KL26-08	431.8	434.8	1.46	14600	0.81	3.1	107	18	2	28	0.01	19	0.2	6.6	44	0.01
KL26-08	434.8	437.8	0.59	5900	0.47	2.1	50	13	2	62	0.01	15	0.3	7.5	42	0.01
KL26-08	437.8	440.8	1.14	11400	0.63	12.1	211	68	980	34	6	17	78	10.0	25	0.23
KL26-08	440.8	443.8	0.58	5800	0.64	1.9	56	40	19	580	4	20	7.3	15.9	29	0.11
KL26-08	443.8	445.2	1.07	10700	0.7	3.1	101	24	3	2300	0.01	13	0.8	9.8	54	0.01
KL26-08	445.2	446.8	0.48	4800	0.33	2.4	97	28	7	52	0.01	17	0.2	9.5	48	0.01
KL26-08	446.8	449.8	0.459	4590	0.42	2.8	94	17	2	44	2	10	0.3	7.8	54	0.01
KL26-08	449.8	453.4	0.52	5200	0.33	3.1	73	21	6	2980	0.01	10	0.6	9.5	67	0.01
KL26-08	453.4	456.8	0.8	8000	0.65	3	58	33	16	53	2	8	2.4	8.8	75	0.01
KL26-08	456.8	458.8	0.265	2650	0.78	2.5	44	48	48	24	18	9	15.5	36.5	82	0.01
KL26-08	458.8	461.8	0.55	5500	0.3	2	118	56	12	19	3	6	1.9	9.0	81	0.01
KL26-08	461.8	464.8	1.05	10500	0.42	2.8	89	39	2	31	0.01	6	0.3	4.7	101	0.01
KL26-08	464.8	467.8	0.68	6800	0.33	1.1	83	43	0.01	14	0.01	7	0.4	6.0	180	0.01
KL26-08	467.8	470.8	0.62	6200	0.33	1	110	17	0.01	16	0.01	13	0.01	7.0	176	0.01
KL26-08	470.8	473.8	0.68	6800	0.48	1.1	75	21	0.01	20	0.01	14	3	6.8	340	0.01
KL26-08	473.8	476.8	0.61	6100	0.35	1.4	123	68	0.01	12	0.01	11	0.6	6.3	305	0.01
KL26-08	476.8	479.8	0.93	9300	0.65	1.9	67	17	0.01	13	0.01	12	0.4	3.8	313	0.01
KL26-08	479.8	482.8	0.64	6400	0.3	0.9	81	48	4	8	0.01	6	0.7	4.8	390	0.01
KL26-08	482.8	485.8	0.374	3740	0.12	1	89	50	3	37	1	4	0.9	3.1	328	0.01
KL26-08	485.8	488.8	0.319	3190	0.1	1	74	32	8	34	0.01	4	0.9	4.0	270	0.01
KL26-08	488.8	494.8	0.524	5240	0.12	1.4	73	34	2	37	1	5	1.8	4.8	393	0.01
KL26-08	494.8	497.8	0.57	5700	0.25	1.9	115	42	1	24	1	5	1	5.8	288	0.01
KL26-08	497.8	500.8	0.462	4620	0.2	2.7	63	38	150	13	5	7	3.6	6.5	328	0.01
KL26-08	500.8	503.8	0.54	5400	0.22	1.7	58	32	0.01	17	1	5	0.5	5.0	335	0.01
KL26-08	503.8	506.8	0.277	2770	0.12	0.7	18	13	3	12	0.01	4	1.6	5.1	411	0.01
KL26-08	506.8	509.8	0.439	4390	0.16	1	14	10	0.01	13	2	6	0.7	5.1	379	0.01
KL26-08	509.8	512.8	0.26	2600	0.15	0.1	44	22	43	23	2	4	4.8	6.2	347	0.01
KL26-08	512.8	515.8	0.74	7400	0.36	1.5	91	32	6	19	0.01	7	0.8	5.3	335	0.01
KL26-08	515.8	518.8	0.71	7100	0.48	1.7	83	77	1	14	1	5	1.3	4.5	393	0.01
KL26-08	518.8	520.9	0.367	3670	0.11	1	50	22	7	8	0.01	3	2.5	3.8	440	0.01
KL26-08	520.9	523.9	0.3	3000	0.26	1.1	62	42	130	3	9	4	18.1	2.5	254	0.01
KL26-08	523.9	525.8	0.24	2400	0.13	1.2	35	16	30	7	3	5	6.1	19.8	540	0.01
KL26-08	525.8	527.8	0.13	1300	0.1	0.8	40	30	39	10	1	6	7.6	12.8	540	0.01
KL26-08	527.8	530.8	0.394	3940	0.39	1.1	22	18	21	30	2	6	2.8	5.8	339	0.01
KL26-08	530.8	533.8	0.91	9100	0.53	4.3	44	12	10	38	2	14	2.3	7.3	305	0.01
KL26-08	533.8	536.8	0.4	4000	0.23	0.8	50	17	2	21	0.01	10	0.4	4.6	340	0.01
KL26-08	536.8	539.8	0.516	5160	0.28	2.7	66	42	5	21	4	9	0.8	4.1	99	0.01
KL26-08	539.8	542.8	0.495	4950	0.35	1.6	42	28	15	20	1	11	1.5	7.3	420	0.01
KL26-08	542.8	545.8	0.56	5600	0.25	3	910	383	2	13	0.01	10	0.9	7.0	406	0.01
KL26-08	545.8	548.8	0.56	5600	0.47	1	72	42	3	11	0.01	7	0.8	5.8	328	0.01
KL26-08	548.8	551.8	0.58	5800	0.5	1.9	46	25	0.01	7	2	6	0.7	5.5	350	0.01
KL26-08	551.8	554.8	0.367	3670	0.36	1.1	175	66	0.01	8	0.01	4	0.2	3.2	156	0.01
KL26-08	554.8	557.8	0.384	3840	0.44	0.7	47	20	0.01	15	0.01	5	0.01	3.5	180	0.01
KL26-08	557.8	560.8	0.41	4100	0.33	0.7	30	13	1	45	0.01	7	0.01	2.9	158	0.01
KL26-08	560.8	563.8	0.34	3400	0.26	0.7	174	27	1	12	0.01	9	0.01	3.2	294	0.01
KL26-08	563.8	566.8	0.318	3180	0.27	0.6	32	13	2	9	0.01	6	0.01	2.4	144	0.01
KL26-08	566.8	569.8	0.56	5600	0.38	1.1	41	17	2	25	0.01	9	1.1	5.0	331	0.01
KL26-08	569.8	572.8	0.56	5600	0.4	1.2	58	19	1	15	0.01	9	0.7	6.0	304	0.01
KL26-08	572.8	575.8	0.32	3200	0.25	0.8	61	25	2	11	0.01	6	0.3	2.9	199	0.01
KL26-08	575.8	578.8	0.478	4780	0.33	1.2	94	38	2	7	0.01	5	0.2	3.1	91	0.01
KL26-08	578.8	580.5	0.393	3930	0.17	1.3	236	82	2	6	0.01	9	0.5	3.6	122	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL26-08	580.5	583.6	0.261		2610	0.29	0.7	138	72	2	4	0.01	6	0.01	2.5	178	0.01
KL26-08	583.6	584.8	0.153		1530	0.13	0.1	36	15	1	9	0.01	3	0.01	1.7	148	0.01
KL26-08	584.8	587.8	0.367		3670	0.32	0.8	77	26	1	5	0.01	6	0.01	2.5	165	0.01
KL26-08	587.8	590.8	0.294		2940	0.27	0.6	43	18	2	5	0.01	5	0.3	2.3	332	0.01
KL26-08	590.8	593.8	0.506		5060	0.25	1.4	59	24	44	10	6	6	1.5	3.3	323	0.01
KL26-08	593.8	596.8	0.325		3250	0.26	1.5	295	170	22	58	5	7	1.4	3.1	217	0.01
KL26-08	596.8	599.8	0.416		4160	0.27	1	107	18	2	20	0.01	7	0.01	3.5	137	0.01
KL26-08	599.8	602.8	0.487		4870	0.32	1.4	141	66	6	13	0.01	6	2.7	3.6	354	0.01
KL26-08	602.8	605.8	0.339		3390	0.22	1.1	159	62	5	9	0.01	6	0.6	3.3	289	0.01
KL26-08	605.8	608.8	0.309		3090	0.22	0.8	44	15	1	15	0.01	7	0.2	2.6	159	0.01
KL26-08	608.8	611.8	0.369		3690	0.2	0.8	59	23	2	30	0.01	7	0.3	2.7	148	0.01
KL26-08	611.8	614.8	0.363		3630	0.24	0.9	40	10	0.01	19	0.01	6	0.2	3.0	165	0.01
KL26-08	614.8	617.8	0.424		4240	0.29	1.1	37	13	2	36	0.01	7	0.3	2.4	410	0.01
KL26-08	617.8	620.8	0.482		4820	0.21	0.9	40	12	1	82	0.01	8	0.01	4.5	160	0.01
KL26-08	620.8	623.8	0.49		4900	0.25	1.3	85	45	300	36	0.01	7	3.7	3.1	138	0.01
KL26-08	623.8	626.8	0.236		2360	0.14	0.7	80	18	18	12	0.01	6	0.01	2.4	116	0.01
KL26-08	626.8	629.8	0.187		1870	0.1	0.6	76	18	3	23	0.01	5	0.01	2.0	103	0.01
KL26-08	629.8	632.8	0.205		2050	0.09	0.1	55	15	3	73	0.01	5	0.01	2.0	97	0.01
KL26-08	632.8	635.8	0.31		3100	0.09	1.2	89	42	14	16	0.01	8	2.1	3.2	160	0.01
KL26-08	635.8	638.8	0.223		2230	0.07	0.6	76	24	1	15	0.01	6	0.3	3.0	105	0.01
KL26-08	638.8	641.8	0.274		2740	0.18	0.8	40	21	2	12	0.01	8	0.2	3.0	103	0.01
KL26-08	641.8	644.8	0.308		3080	0.18	0.8	53	34	1	18	0.01	7	0.01	2.4	125	0.01
KL26-08	644.8	647.8	0.3		3000	0.16	0.8	70	70	2	6	0.01	6	0.2	3.3	124	0.01
KL26-08	647.8	650.8	0.309		3090	0.18	0.7	59	22	0.01	9	0.01	7	0.01	3.0	136	0.01
KL26-08	650.8	653.8	0.287		2870	0.14	0.8	84	29	0.01	9	0.01	7	0.01	2.2	104	0.01
KL26-08	653.8	656.8	0.359		3590	0.08	1.5	226	68	75	73	1	7	2.1	2.7	87	0.01
KL26-08	656.8	659.8	0.273		2730	0.12	0.7	86	23	3	17	0.01	5	0.01	3.1	103	0.01
KL26-08	659.8	662.8	0.4		4000	0.25	1.1	490	162	350	16	2	11	36	3.4	72	0.01
KL26-08	662.8	665.8	0.253		2530	0.09	1.2	193	129	390	30	2	8	27	3.6	82	0.44
KL26-08	665.8	668.8	0.235		2350	0.05	0.8	108	78	80	25	0.01	4	6.4	3.2	108	0.1
KL26-08	668.8	671.8	0.434		4340	0.18	0.7	46	25	4	16	0.01	5	0.4	2.8	124	0.01
KL26-08	671.8	674.8	0.25		2500	0.11	0.6	63	32	4	23	0.01	6	0.7	2.5	281	0.01
KL26-08	674.8	677.8	0.23		2300	0.08	0.6	113	51	25	18	1	8	1.7	1.8	95	0.01
KL26-08	677.8	680.8	0.23		2300	0.07	0.6	66	41	1	21	0.01	9	0.5	2.6	121	0.01
KL26-08	680.8	683.8	0.286		2860	0.08	0.8	128	66	45	30	0.01	7	1.9	2.4	120	0.01
KL26-08	683.8	686.8	0.194		1940	0.05	0.1	87	43	2	13	0.01	8	0.3	1.6	125	0.01
KL26-08	686.8	689.8	0.18		1800	0.03	0.1	54	39	1	15	0.01	6	0.7	2.0	127	0.01
KL26-09	0	4	0.003		30	0.01	0.1	49	48	7	1	0.01	1	0.6	2.1	25	0.01
KL26-09	4	7	0.0024		24	0.01	0.1	49	38	4	2	0.01	1	0.7	2.3	27	0.01
KL26-09	7	10	0.0022		22	0.01	0.1	29	16	4	1	0.01	1	0.2	3.5	43	0.01
KL26-09	10	13	0.003		30	0.01	0.1	20	15	3	3	0.01	1	0.3	1.5	30	0.01
KL26-09	13	16	0.0025		25	0.01	0.1	19	16	6	1	0.01	1	0.5	2.0	25	0.01
KL26-09	16	19	0.0074		74	0.04	0.1	35	23	4	4	0.01	1	0.5	1.5	26	0.01
KL26-09	19	22	0.0022		22	0.01	0.1	47	24	5	2	0.01	1	0.4	3.3	27	0.01
KL26-09	22	25	0.0108		108	0.01	0.1	39	53	6	3	0.01	1	0.5	1.3	38	0.01
KL26-09	25	28	0.0172		172	0.01	0.1	48	182	8	5	0.01	2	0.8	3.5	57	0.01
KL26-09	28	31	0.0059		59	0.01	0.6	43	63	14	5	0.01	4	1.8	3.3	88	0.01
KL26-09	31	34	0.0232		232	0.13	0.9	230	170	45	14	0.01	5	3	5.0	100	0.01
KL26-09	34	37	0.078		780	0.79	40	10600	8000	200	10	7	3	21.5	155.0	32	0.26
KL26-09	37	40	0.0269		269	0.13	8.6	2400	1560	73	17	6	1	5.8	71.3	39	0.01
KL26-09	40	42.5	0.022		220	0.61	27.8	8500	5300	150	48	15	1	8.5	44.8	95	0.1
KL26-09	42.5	45.3	0.17		1700	0.04	0.8	59	25	7	1160	0.01	21	0.4	0.0	18	0.01
KL26-09	45.3	48.3	0.005		50	0.09	1.6	206	1120	15	18	0.01	1	5	3.5	40	0.01
KL26-09	48.3	51.5	0.0146		146	0.08	1	128	680	20	21	0.01	1	3	4.0	96	0.01
KL26-09	51.5	53.7	0.0046		46	0.01	0.6	134	1100	8	5	0.01	1	1.5	1.0	60	0.01
KL26-09	53.7	56.5	0.0047		47	0.01	0.5	85	890	16	7	0.01	1	2.6	2.2	58	0.01
KL26-09	56.5	59.7	0.0045		45	0.02	0.1	89	373	9	5	0.01	1	1.8	2.2	44	0.01
KL26-09	59.7	62.5	0.0076		76	0.05	4.3	870	5900	10	3	1	1	6.5	4.5	71	0.01
KL26-09	62.5	65.5	0.0079		79	0.01	1	95	398	7	2	0.01	1	2.3	0.5	17	0.01
KL26-09	65.5	68.5	0.0117		117	0.02	0.9	106	420	7	12	0.01	1	2	0.0	16	0.01
KL26-09	68.5	71.5	0.0091		91	0.03	0.9	51	389	6	12	0.01	1	2.1	2.2	10	0.01
KL26-09	71.5	74.9	0.0053		53	0.01	1.2	59	218	6	9	0.01	1	1.4	1.0	18	0.01
KL26-09	74.9	77.5	0.0094		94	0.01	0.1	29	36	1	3	0.01	1	0.2	0.5	25	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL26-09	77.5	80.5	0.0036		36	0.01	0.1	42	69	8	3	0.01	1	1.5	3.0	15	0.01
KL26-09	80.5	83.5	0.0095		95	0.05	2.6	57	770	24	5	0.01	1	3.9	0.6	40	0.01
KL26-09	83.5	86.5	0.0079		79	0.07	4.6	146	1300	12	6	0.01	1	1.6	2.2	27	0.01
KL26-09	86.5	90.1	0.0067		67	0.03	1.1	76	350	3	6	0.01	1	0.4	1.8	16	0.01
KL26-09	90.1	93.6	0.0088		88	0.06	2.2	174	620	9	9	1	1	1	2.8	17	0.01
KL26-09	93.6	97	0.0067		67	0.02	2.1	271	1030	5	3	0.01	1	1.2	1.8	22	0.01
KL26-09	97	100	0.0111		111	0.05	3.9	128	1470	26	4	0.01	1	1.8	4.9	18	0.01
KL26-09	100	103	0.0062		62	0.06	2.3	27	378	23	3	1	1	1.5	2.5	20	0.01
KL26-09	103	106.6	0.0048		48	0.05	2.5	62	272	18	3	0.01	1	1	3.8	28	0.01
KL26-09	106.6	109.8	0.066		660	0.06	1.8	560	650	10	7	0.01	1	1.1	3.0	34	0.01
KL26-09	109.8	112	0.0048		48	0.02	2.2	39	375	9	3	0.01	1	1.2	1.6	29	0.01
KL26-09	112	115	0.0032		32	0.02	1.7	49	283	7	5	1	1	0.8	3.3	28	0.01
KL26-09	115	118	0.0018		18	0.03	1.3	36	143	2	2	0.01	1	0.5	1.0	30	0.01
KL26-09	118	120.6	0.0037		37	0.04	2.7	44	224	6	4	3	1	0.6	2.5	31	0.01
KL26-09	120.6	123.2	0.0024		24	0.05	2.9	87	295	8	2	3	1	0.8	1.5	30	0.01
KL26-09	123.2	126.5	0.0017		17	0.03	0.9	27	102	4	1	0.01	1	0.3	0.9	29	0.01
KL26-09	126.5	129.1	0.0032		32	0.03	2.3	42	308	6	3	0.01	1	2.6	1.8	36	0.01
KL26-09	129.1	132.4	0.0371		371	0.04	1.3	108	420	4	3	0.01	1	0.6	1.4	35	0.01
KL26-09	132.4	135.4	0.0044		44	0.01	1.1	33	172	5	2	0.01	1	0.4	0.8	27	0.01
KL26-09	135.4	138.4	0.0371		371	0.05	3.5	329	540	12	13	1	1	1.1	3.5	29	0.01
KL26-09	138.4	140.7	0.0017		17	0.06	2.7	265	353	5	5	0.01	1	0.9	2.0	18	0.01
KL26-09	140.7	143	0.0014		14	0.03	2.4	99	325	6	9	0.01	1	0.7	2.5	17	0.01
KL26-09	143	145.6	0.0058		58	0.21	11.1	166	299	35	11	0.01	1	3.1	11.0	16	0.01
KL26-09	145.6	148.1	0.0044		44	0.07	6.2	840	1330	8	10	0.01	1	2.3	4.2	15	0.01
KL26-09	148.1	151	0.0031		31	0.02	2.7	216	352	6	8	0.01	1	1	1.8	22	0.01
KL26-09	151	153.8	0.0019		19	0.01	1.6	102	193	3	6	0.01	1	0.8	1.0	18	0.01
KL26-09	153.8	156.2	0.0016		16	0.01	2.1	220	730	7	3	0.01	1	0.8	1.0	18	0.01
KL26-09	156.2	160	0.0031		31	0.02	2.5	359	660	5	4	0.01	1	1.2	1.5	19	0.01
KL26-09	160	163.1	0.0032		32	0.01	2.6	232	680	4	4	0.01	1	0.9	1.4	14	0.01
KL26-09	163.1	165.7	0.0113		113	0.02	2.6	309	780	4	7	0.01	1	1	2.8	16	0.01
KL26-09	165.7	170.5	0.0025		25	0.01	2.1	102	180	2	3	0.01	1	0.3	1.3	15	0.01
KL26-09	170.5	173.5	0.0045		45	0.02	6.2	77	363	13	3	3	1	0.6	2.2	20	0.01
KL26-09	173.5	176.5	0.002		20	0.03	2	101	164	7	11	0.01	1	1.2	5.8	24	0.01
KL26-09	176.5	179.5	0.0021		21	0.01	1.7	128	118	2	6	0.01	1	1.3	1.3	19	0.01
KL26-09	179.5	182.2	0.0045		45	0.01	1.6	141	128	6	5	0.01	1	0.8	1.2	18	0.01
KL26-09	182.2	188.8	0.0019		19	0.03	1.5	133	168	5	3	0.01	1	0.6	1.4	16	0.01
KL26-09	188.8	193	0.0015		15	0.02	0.7	53	64	5	9	0.01	1	0.3	1.1	17	0.01
KL26-09	193	196	0.0029		29	0.06	1.8	173	234	8	4	0.01	1	0.7	1.5	15	0.01
KL26-09	196	198.5	0.0175		175	0.14	23.3	5800	14800	13	107	3	1	6.3	28.5	21	0.29
KL26-09	198.5	201.5	0.0058		58	0.04	1.6	560	1380	17	17	0.01	1	1.7	1.0	24	0.01
KL26-09	201.5	204.3	0.0316		316	0.1	20	6600	10700	37	12	6	1	13.2	20.3	19	0.48
KL26-09	204.3	208	0.0061		61	0.11	4.2	2700	2450	13	48	8	1	2.1	8.0	18	0.1
KL26-09	208	211	0.0059		59	0.4	17.1	4600	12400	20	72	28	1	3.6	23.0	18	0.19
KL26-09	211	214	0.0017		17	0.08	1.3	157	680	6	15	2	1	0.2	2.0	21	0.01
KL26-09	214	217	0.0029		29	0.06	1.1	950	930	14	9	1	1	0.01	2.2	15	0.01
KL26-09	217	220	0.0219		219	0.14	1.6	860	630	25	21	2	1	0.7	3.5	27	0.15
KL26-09	220	223	0.05		500	0.13	8.2	980	1410	67	16	10	1	3.4	6.3	20	0.13
KL26-09	223	226	1.27		12700	1.09	22.1	13600	2700	140	21	11	15	3.1	32.7	71	0.51
KL26-09	226	229.8	0.189		1890	0.4	5.8	279	109	61	720	92	14	3.9	18.5	81	0.01
KL26-09	229.8	233.4	0.32		3200	0.71	8.1	299	66	120	780	110	6	3.7	11.5	185	0.15
KL26-09	233.4	236.5	0.95		9500	1.92	22.3	168	39	49	1000	96	17	2.1	20.3	65	0.12
KL26-09	236.5	239.5	0.8		8000	1.85	17.3	164	46	29	292	161	10	1.4	47.0	34	0.01
KL26-09	239.5	242.6	1.01		10100	1.67	16.1	104	34	26	1720	165	14	1.5	16.1	33	0.01
KL26-09	242.6	245.5	0.9		9000	1.58	16	162	32	13	470	68	22	1.2	15.3	45	0.01
KL26-09	245.5	248.5	0.88		8800	3.05	25.1	147	31	25	2200	113	21	1.5	13.0	46	0.01
KL26-09	248.5	251.5	0.4		4000	1.4	11.1	107	34	22	118	44	11	1	11.5	53	0.01
KL26-09	251.5	254.5	0.91		9100	1.22	23.4	209	46	30	35	52	18	1	21.3	47	0.01
KL26-09	254.5	257.5	0.54		5400	1.01	11.4	122	57	25	36	34	10	1.6	14.0	27	0.01
KL26-09	257.5	260.5	0.76		7600	2.15	13.3	1420	62	40	8	30	12	2	14.5	38	0.01
KL26-09	260.5	263.5	1.52		15200	2.38	15.7	6700	38	58	17	37	35	1.3	53.8	52	0.01
KL26-09	263.5	266.5	0.49		4900	0.67	3.2	156	32	36	185	10	16	2.3	23.3	48	0.01
KL26-09	266.5	269.5	0.39		3900	0.94	2.9	153	50	30	2160	27	35	3.2	62.8	95	0.01
KL26-09	269.5	272.5	0.35		3500	1.1	4	127	27	32	1550	31	6	2.9	45.3	94	0.15

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL26-09	272.5	274	3.25	32500	4.02	22.4	345	34	130	118	9	101	2	33.0	84	0.32
KL26-09	274	277	2.79	27900	2.18	20.9	347	27	220	26	49	73	0.7	32.0	83	0.39
KL26-09	277	280	2.97	29700	3.72	20.7	770	26	180	118	78	69	0.8	35.0	149	0.58
KL26-09	280	283	1.2	12000	1.4	9.5	247	38	54	680	55	16	1.2	56.0	138	0.21
KL26-09	283	286	1.99	19900	2.66	13.2	334	81	80	207	104	87	1.6	64.0	121	0.38
KL26-09	286	289	1.47	14700	2.44	10.7	289	46	80	260	52	70	1.2	68.0	182	0.72
KL26-09	289	292	3	30000	2.5	19.8	362	46	220	64	56	200	0.7	44.0	89	0.75
KL26-09	292	295	1.01	10100	1.84	12.8	200	30	54	690	31	62	0.5	73.0	225	0.57
KL26-09	295	298	2.29	22900	2.7	15.7	245	26	65	395	48	113	0.5	59.0	107	0.71
KL26-09	298	300.3	2.61	26100	3.86	23.7	418	118	85	1150	57	71	1.9	34.0	112	0.23
KL26-09	300.3	303.3	2.12	21200	4.48	18.8	490	198	170	1570	33	122	1.9	69.5	185	0.16
KL26-09	303.3	305.3	4.74	47400	3.6	31.9	600	32	68	72	57	287	0.7	30.0	190	0.17
KL26-09	305.3	306.9	5.3	53000	2.58	31	860	36	100	210	56	288	1.3	26.3	80	0.21
KL26-09	306.9	308.5	1.5	15000	1.5	12.3	2010	37	250	15	37	237	2.4	30.0	56	0.18
KL26-09	308.5	311.5	1.26	12600	1.98	14.5	7100	34	260	97	34	220	3.5	47.3	101	0.56
KL26-09	311.5	314.5	1.25	12500	1.5	9.8	580	24	23	5	21	69	1.2	15.2	55	0.17
KL26-09	314.5	319.5	2.72	27200	1.94	21.4	3000	164	190	173	41	63	2.4	41.0	141	0.72
KL26-09	319.5	321.7	0.56	5600	1.68	7.3	1600	407	500	200	1430	6	16	56.0	130	0.36
KL26-09	321.7	324.3	0.88	8800	2.7	9.9	880	331	310	1510	140	11	10.9	49.5	76	0.37
KL26-09	324.3	329.5	1	10000	1.62	9.5	4600	300	370	252	112	31	3.1	80.0	70	0.28
KL26-09	329.5	330.7	0.165	1650	0.49	9.8	14400	1100	450	146	54	4	3.8	24.5	41	0.1
KL26-09	330.7	334	0.51	5100	1.12	11.8	10300	2100	370	308	140	14	4.1	87.5	91	0.16
KL26-09	334	340	0.42	4200	0.79	10.9	10400	2400	180	104	56	8	3.4	43.0	53	0.19
KL26-09	361	364	0.041	410	0.26	7.7	3400	3800	180	64	21	4	3.8	40.1	18	0.01
KL26-09	364	367	0.0103	103	0.06	0.1	270	148	10	8	2	1	0.4	2.3	14	0.01
KL26-09	367	370	0.0062	62	0.06	0.5	268	95	11	20	20	1	0.4	3.8	14	0.01
KL26-09	370	372	1.91	19100	1.42	9.6	1270	84	10	7	5	35	0.5	19.0	18	0.01
KL26-09	372	376	2.23	22300	1.44	34	2080	1030	43	88	5	25	0.7	10.0	14	0.01
KL26-09	376	379	0.0362	362	0.06	1.4	274	214	14	27	4	3	1.9	2.3	11	0.01
KL26-09	379	382	0.0166	166	0.07	1.9	401	200	12	34	46	1	1	2.9	12	0.01
KL26-09	382	386.3	0.0101	101	0.05	1.4	316	172	10	18	30	1	0.3	2.1	14	0.01
KL26-09	386.3	389.3	0.0261	261	0.14	12.1	5000	10300	37	40	16	2	6.2	53.0	18	0.01
KL26-09	389.3	392.3	0.0074	74	0.07	1.1	980	460	22	19	2	2	0.8	2.0	19	0.01
KL26-09	392.3	395.3	0.004	40	0.04	0.6	120	110	12	7	0.01	1	0.4	1.8	14	0.01
KL26-09	395.3	398.3	0.0094	94	0.05	1.1	378	610	16	25	2	3	0.8	4.8	15	0.01
KL26-09	398.3	401.3	0.0042	42	0.01	0.1	121	54	10	18	1	2	0.01	1.5	16	0.01
KL26-09	401.3	404.3	0.0045	45	0.02	0.1	95	48	11	4	0.01	2	0.2	2.3	15	0.01
KL26-09	404.3	407.3	0.0076	76	0.03	0.1	60	59	22	8	0.01	3	1	0.9	18	0.01
KL26-09	407.3	410	0.0045	45	0.06	0.1	73	45	34	2	0.01	2	0.7	1.8	18	0.01
KL26-09	410	413.1	0.0024	24	0.06	0.1	56	32	30	1	0.01	2	0.8	1.3	20	0.01
KL26-09	413.1	416.3	0.0031	31	0.09	0.1	120	51	40	1	0.01	1	0.9	1.7	24	0.01
KL26-09	416.3	418.1	0.0108	108	0.04	0.8	171	87	21	6	1	1	0.6	3.7	15	0.01
KL26-10	0	2.3	0.0123	123	0.02	0.1	40	31	10	1	0.01	1	1.2	1.3	22	0.01
KL26-10	2.3	4.3	0.0038	38	0.01	0.1	52	47	6	1	0.01	1	1.6	1.1	20	0.01
KL26-10	4.3	7.3	0.0053	53	0.02	0.1	45	51	10	1	1	1	1.7	1.3	21	0.01
KL26-10	7.3	10.3	0.0194	194	0.14	24.2	4900	3000	68	10	40	1	13.8	12.1	19	0.17
KL26-10	10.3	13.3	0.0065	65	0.01	0.8	46	107	8	10	0.01	1	2.9	2.3	25	0.01
KL26-10	13.3	16.3	0.0051	51	0.02	0.1	50	50	4	1	0.01	1	1	1.3	32	0.11
KL26-10	16.3	19.3	0.0067	67	0.02	0.1	21	26	7	1	0.01	1	1.1	0.8	34	0.1
KL26-10	19.3	22.3	0.0048	48	0.01	0.1	35	34	7	1	0.01	1	0.9	1.2	27	0.01
KL26-10	22.3	25.3	0.0026	26	0.03	0.1	24	42	3	1	0.01	1	0.4	1.7	26	0.01
KL26-10	25.3	28.3	0.0034	34	0.03	0.9	31	124	4	1	0.01	1	0.8	2.0	18	0.01
KL26-10	28.3	31.3	0.003	30	0.01	0.7	22	61	3	1	0.01	1	0.4	1.2	23	0.01
KL26-10	31.3	32.8	0.0068	68	0.01	0.1	36	64	2	1	0.01	1	0.7	1.6	24	0.01
KL26-10	32.8	35.8	0.014	140	0.01	0.1	25	21	6	1	0.01	1	0.4	2.1	36	0.01
KL26-10	35.8	37.3	0.0041	41	0.01	0.1	20	25	12	1	0.01	1	0.5	1.0	22	0.01
KL26-10	37.3	40.3	0.0023	23	0.01	0.1	25	20	4	1	0.01	1	0.7	2.1	23	0.01
KL26-10	40.3	43.3	0.0045	45	0.01	1.8	114	309	7	1	3	2	0.8	8.7	20	0.01
KL26-10	43.3	44.8	0.0075	75	0.01	0.1	80	31	13	1	0.01	3	0.4	0.6	48	0.01
KL26-10	44.8	47.8	0.0025	25	0.03	1.5	172	132	7	1	0.01	2	1.1	2.2	74	0.01
KL26-10	47.8	50.8	0.0067	67	0.01	0.1	57	45	6	1	0.01	2	0.8	1.0	44	0.01
KL26-10	50.8	53.8	0.004	40	0.01	0.1	34	35	9	1	0.01	2	1.7	1.5	126	0.01
KL26-10	53.8	56.8	0.041	410	0.01	1.4	56	630	30	7	0.01	5	2.2	3.1	122	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL26-10	56.8	58.4	0.0352		352	0.13	18.7	600	3700	51	4	16	5	6.1	21.8	86	0.01
KL26-10	58.4	61.6	0.0074		74	0.01	7	1410	2600	17	1	9	1	3.6	4.8	12	0.01
KL26-10	61.6	64.6	0.0051		51	0.07	6.7	1700	4800	11	20	2	1	6.3	3.7	17	0.01
KL26-10	64.6	67.3	0.0078		78	0.12	13.4	394	1970	10	16	20	1	5.5	43.0	27	0.01
KL26-10	67.3	70.3	0.0098		980	0.92	139	4000	26300	130	15	74	1	25	124.0	64	0.01
KL26-10	70.3	76.3	0.0217		217	0.29	10.6	167	710	44	10	26	1	2	7.0	28	0.01
KL26-10	76.3	80.6	0.0176		176	0.07	13.8	376	1090	4	10	30	1	0.8	7.7	52	0.01
KL26-10	80.6	82.9	0.0147		147	0.09	1.4	41	105	15	20	2	1	1	1.1	36	0.01
KL26-10	82.9	85.6	0.0035		35	0.07	0.8	46	65	23	10	0.01	1	1.1	0.0	113	0.01
KL26-10	85.6	88.3	0.0049		49	0.03	0.1	61	80	15	2	0.01	1	0.7	0.0	170	0.01
KL26-10	88.3	91.3	0.0126		126	0.07	3.1	319	540	24	4	2	1	2.7	2.6	145	0.01
KL26-10	91.3	94.3	0.0033		33	0.01	0.1	45	110	3	2	0.01	1	0.5	0.0	205	0.01
KL26-10	94.3	97.3	0.004		40	0.01	0.8	123	68	16	8	0.01	1	2.4	0.0	87	0.01
KL26-10	97.3	100.3	0.0074		74	0.01	0.8	115	120	9	12	0.01	1	2.7	0.0	53	0.01
KL26-10	100.3	103.3	0.007		70	0.01	0.7	75	157	5	6	0.01	1	1.7	0.0	118	0.01
KL26-10	103.3	104.7	0.0038		38	0.01	0.7	186	240	2	4	0.01	1	0.7	1.0	177	0.01
KL26-10	104.7	107.8	0.0013		13	0.01	0.7	63	307	4	4	0.01	1	1.5	0.5	108	0.01
KL26-10	107.8	110.8	0.0016		16	0.01	0.1	92	54	2	3	0.01	1	0.5	1.0	162	0.01
KL26-10	110.8	113.8	0.0019		19	0.01	0.1	85	100	2	4	0.01	1	0.6	0.8	117	0.01
KL26-10	113.8	116.8	0.0018		18	0.01	0.1	24	27	2	4	0.01	1	0.3	0.0	97	0.01
KL26-10	116.8	119.8	0.0023		23	0.01	0.1	35	50	2	6	0.01	1	0.5	1.0	84	0.01
KL26-10	119.8	122.8	0.0014		14	0.01	0.1	20	27	2	3	0.01	1	0.01	0.0	65	0.01
KL26-10	122.8	125.8	0.0053		53	0.01	0.1	20	25	3	7	0.01	1	0.01	0.0	12	0.01
KL26-10	125.8	127.3	0.0041		41	0.01	0.1	32	54	5	8	0.01	1	0.6	0.0	11	0.01
KL26-10	127.3	129.3	0.0055		55	0.01	1.7	132	174	22	4	0.01	1	4.3	0.0	12	0.01
KL26-10	129.3	131.4	0.0068		68	0.01	1.4	94	134	7	7	0.01	1	1.5	0.0	11	0.01
KL26-10	131.4	134.6	0.003		30	0.01	0.1	35	61	4	6	0.01	1	0.5	0.0	11	0.01
KL26-10	134.6	137.5	0.0034		34	0.01	0.1	26	27	4	2	0.01	1	0.01	0.0	11	0.01
KL26-10	137.5	139.9	0.0036		36	0.01	1.2	69	78	7	3	0.01	1	1.3	0.6	14	0.01
KL26-10	139.9	142.7	0.0058		58	0.05	0.5	103	150	5	1	0.01	1	0.9	0.0	19	0.01
KL26-10	142.7	145.1	0.0115		115	0.6	12	470	780	36	15	0.01	1	8.6	3.2	30	0.01
KL26-10	145.1	148.3	0.0045		45	0.15	2.5	730	730	8	7	0.01	1	5	2.8	33	0.01
KL26-10	148.3	151.3	0.0028		28	0.21	1.5	450	570	4	1	0.01	1	3.8	2.4	23	0.01
KL26-10	151.3	154.3	0.0034		34	0.34	1.4	78	184	3	4	0.01	1	3.2	1.8	19	0.01
KL26-10	154.3	156.7	0.0033		33	0.3	1.5	105	165	24	2	0.01	1	3.4	2.1	24	0.01
KL26-10	156.7	159.9	0.014		140	0.1	19	7600	7300	19	5	0.01	1	13.9	5.4	21	0.15
KL26-10	159.9	162	0.006		60	0.06	3.3	92	321	35	4	0.01	1	2	1.3	23	0.01
KL26-10	162	164.8	0.0085		85	0.13	12.7	220	384	290	6	0.01	1	3.3	1.4	24	0.01
KL26-10	164.8	167.6	0.0065		65	0.05	8.2	810	2070	8	1	0.01	1	4.5	2.6	19	0.01
KL26-10	167.6	170.8	0.0135		135	0.01	33	710	6400	28	1	0.01	1	18.6	4.4	23	0.01
KL26-10	170.8	173.8	0.0084		84	0.03	32	2800	13300	14	1	0.01	1	25.8	4.4	24	0.01
KL26-10	173.8	176.8	0.002		20	0.02	1	32	162	5	2	0.01	1	1.2	0.0	19	0.01
KL26-10	176.8	178.3	0.0031		31	0.04	3.8	590	780	5	6	1	1	7.4	1.3	24	0.01
KL26-10	178.3	181.1	0.0034		34	0.05	4.7	179	1110	6	3	2	1	4.9	1.3	26	0.01
KL26-10	181.1	184.2	0.0081		81	0.04	12.1	73	1880	27	4	1	1	6	2.1	24	0.01
KL26-10	184.2	186.8	0.0074		74	0.04	10.1	1000	2700	37	1	0.01	1	9.2	3.1	21	0.01
KL26-10	186.8	189.8	0.004		40	0.03	3.3	120	650	14	1	1	1	5.3	1.4	29	0.01
KL26-10	189.8	191.4	0.045		450	0.1	72	18500	3700	140	3	1	1	42.5	6.7	28	0.7
KL26-10	191.4	194.6	0.0114		114	0.02	11	175	193	41	3	3	1	5	3.5	20	0.01
KL26-10	194.6	196.2	0.0054		54	0.03	2.5	158	257	13	4	3	1	1.4	1.3	24	0.01
KL26-10	196.2	199.3	0.004		40	0.03	3.2	303	185	15	5	2	1	1.7	1.2	22	0.01
KL26-10	199.3	202.3	0.0025		25	0.04	1.7	46	140	9	21	3	1	1.2	1.4	27	0.01
KL26-10	202.3	204.4	0.0025		25	0.16	3.1	378	620	40	32	2	1	6.8	1.6	36	0.01
KL26-10	204.4	210	0.0114		114	0.1	31	7900	5500	25	37	5	1	38.3	9.4	30	0.23
KL26-10	210	213	0.0058		58	0.04	2.7	620	430	8	8	3	1	2.3	2.5	23	0.01
KL26-10	213	216	0.0075		75	0.05	4.3	670	2600	14	18	1	1	4.7	2.3	13	0.01
KL26-10	216	219	0.005		50	0.05	4.4	930	2100	12	6	1	1	3.2	3.3	11	0.01
KL26-10	219	222.2	0.0031		31	0.06	1.4	355	500	4	5	0.01	1	1.4	1.6	12	0.01
KL26-10	222.2	226	0.0037		37	0.04	3.2	980	1540	9	17	0.01	1	3.1	0.9	10	0.01
KL26-10	226	229	0.0032		32	0.03	1.3	170	650	8	7	0.01	1	1.5	0.6	11	0.01
KL26-10	229	231	0.0048		48	0.04	1.6	550	810	9	13	0.01	1	1.8	1.1	9	0.01
KL26-10	231	234	0.0054		54	0.09	1.2	560	740	9	84	0.01	1	4.1	2.3	16	0.01
KL26-10	234	237.2	0.0043		43	0.04	1.1	420	530	12	39	2	1	0.9	1.8	13	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL26-10	237.2	240	0.0047		47	0.03	1.4	660	770	8	36	1	1	1.6	1.9	10	0.01
KL26-10	240	242.7	0.0059		59	0.03	1.1	167	261	13	32	2	1	0.8	1.2	10	0.01
KL26-10	242.7	245	0.0055		55	0.02	1.4	162	970	8	32	2	1	1.5	1.5	12	0.01
KL26-10	245	247	0.0093		93	0.08	1.9	940	1100	9	95	2	1	1.3	1.3	11	0.01
KL26-10	247	249.6	0.0104		104	0.02	12	730	3800	25	63	26	1	3.2	8.4	10	0.01
KL26-10	249.6	252	0.0093		93	0.04	2.6	630	1290	11	67	4	1	2	3.5	13	0.01
KL26-10	252	255	0.0119		119	0.02	5.2	1610	2500	12	32	7	1	3.9	3.4	10	0.01
KL26-10	255	258	0.0034		34	0.11	0.9	260	274	16	21	1	1	1.4	2.5	14	0.01
KL26-10	258	261	0.0166		166	0.05	4.6	1850	2000	30	73	3	1	5	4.3	11	0.01
KL26-10	261	264	0.0178		178	0.07	3.5	1010	388	31	147	3	1	3.4	2.6	10	0.1
KL26-10	264	267	0.0421		421	0.07	5.7	1870	510	89	215	5	2	10.3	4.5	11	0.13
KL26-10	267	270	0.24		2400	0.48	30	12100	8300	250	537	32	7	22	26.3	30	0.24
KL26-10	270	272	0.06		600	0.12	11.4	4590	1020	150	690	7	8	16	9.1	22	0.22
KL26-10	272	274.6	0.048		480	0.11	4.3	1030	401	150	870	7	3	13.4	5.8	26	0.01
KL26-10	274.6	277	0.072		720	0.08	8.9	4270	1030	210	447	12	4	18.2	7.5	18	0.17
KL26-10	277	279.8	0.097		970	0.13	8.1	6800	550	270	800	7	6	26	6.8	16	0.34
KL26-10	279.8	283	0.091		910	0.15	9.4	4810	2030	150	749	14	6	12.8	12.6	23	0.35
KL26-10	283	285.9	0.073		730	0.12	16.9	3650	1550	170	690	6	4	34	7.8	16	0.12
KL26-10	285.9	288	0.091		910	0.15	11.3	5120	1730	170	650	9	5	21	10.5	19	0.16
KL26-10	288	291	0.047		470	0.11	9.1	3340	1570	120	660	8	4	21	8.5	15	0.01
KL26-10	291	294	0.065		650	0.14	17.9	5030	1660	160	970	8	9	33	9.3	13	0.12
KL26-10	294	297	0.166		1660	0.52	30.8	6800	3800	100	387	8	15	45	25.5	30	0.14
KL26-10	297	300	0.075		750	0.18	40	17200	11400	160	810	6	7	26	12.5	29	0.18
KL26-10	300	303	0.11		1100	0.17	49	11900	8700	110	1270	20	9	21	11.0	29	0.01
KL26-10	303	306	0.064		640	0.09	12.5	2780	4730	60	840	7	7	9.5	16.8	26	0.01
KL26-10	306	309	0.077		770	0.1	36	17500	5800	44	407	53	5	5.6	49.0	28	0.14
KL26-10	309	312	0.31		3100	0.13	27.2	14400	13300	64	990	22	20	8	6.0	39	0.51
KL26-10	312	315	0.85		8500	0.2	38	12800	7900	100	740	27	34	4.5	16.3	32	0.68
KL26-10	315	318	0.095		950	0.19	14	4770	3090	99	650	14	9	10	18.5	24	0.41
KL26-10	318	321	0.156		1560	0.2	17.2	10300	9100	47	305	19	6	3.9	30.5	37	0.23
KL26-10	321	322.5	0.144		1440	0.25	16.2	9000	8800	110	67	23	9	4.5	15.5	26	0.22
KL26-10	322.5	324	1.83		18300	1.82	91	82000	17500	500	397	223	68	9.5	263.0	80	1.3
KL26-10	324	327	0.88		8800	0.78	30	23900	1310	350	399	110	19	4.8	178.0	143	0.25
KL26-10	327	330	0.48		4800	1.96	78	121000	30300	190	141	184	36	14.1	302.0	111	0.12
KL26-10	330	333	0.67		6700	1.46	132	95000	24900	260	150	410	28	5.3	313.0	91	0.19
KL26-10	333	334.4	0.47		4700	0.84	8.5	14900	1600	200	2170	24	57	4.9	88.0	112	0.1
KL26-10	334.4	336	0.081		810	0.16	3.5	1770	1680	58	328	12	4	2.1	24.0	81	0.01
KL26-10	336	339	0.176		1760	0.37	13.6	15800	5900	65	550	19	12	6.3	48.0	63	0.01
KL26-10	339	341.5	0.209		2090	0.58	7.3	3040	1470	90	870	30	7	2.9	56.2	74	0.01
KL26-10	341.5	343.2	0.8		8000	1.35	136	120000	104600	280	880	136	21	110	120.0	88	0.28
KL26-10	343.2	345	0.24		2400	0.92	45	35300	29100	170	770	59	12	30	79.5	80	0.1
KL26-10	345	348	0.068		680	0.43	32.4	15800	19600	110	167	30	14	18	60.0	44	0.01
KL26-10	348	351	0.48		4800	1	65	22000	19100	360	364	44	15	22	51.0	33	0.01
KL26-10	351	354	0.158		1580	0.44	41	42100	15700	130	540	78	8	17.2	46.0	45	0.11
KL26-10	354	357	0.0224		224	0.7	12.5	4200	8900	61	156	6	3	9.4	22.0	51	0.01
KL26-10	357	360	0.33		3300	1.18	33	8800	3300	140	640	10	20	70	42.0	51	0.36
KL26-10	360	363	0.41		4100	0.7	43	49700	19800	200	470	38	37	24	86.5	71	0.01
KL26-10	363	366	0.0312		312	0.17	8.4	7500	2790	48	60	4	3	4.9	9.0	27	0.01
KL26-10	366	369	0.073		730	0.24	26.4	21600	10700	110	157	15	6	20	86.0	29	0.17
KL26-10	369	372	0.074		740	0.13	12.7	9500	5200	160	490	7	5	22	71.8	18	0.23
KL26-10	372	375	0.0281		281	0.37	8.3	4090	4100	41	100	4	3	5.2	9.5	45	0.01
KL26-10	375	378	0.0315		315	1.02	10.6	5320	7300	83	78	5	2	6.5	22.3	48	0.01
KL26-10	378	381	0.02		200	0.15	12.3	10900	7500	17	60	28	5	5.8	58.8	20	0.01
KL26-10	381	384	0.0379		379	0.17	10.5	8400	14000	17	112	15	1	3.9	71.0	19	0.01
KL26-10	384	387	0.0215		215	0.13	9.9	9100	6700	19	59	26	2	5	47.0	22	0.01
KL26-10	387	390	0.0179		179	0.15	4	2740	2160	26	40	3	1	3.5	6.3	28	0.01
KL26-10	390	393	0.09		900	0.23	24.2	21300	9800	90	384	50	3	11	38.5	37	0.01
KL26-10	393	396	0.0056		56	0.02	0.9	590	326	17	13	1	1	1.3	0.0	20	0.01
KL26-10	396	399	0.0062		62	0.03	0.9	247	187	13	25	2	1	0.5	0.8	18	0.01
KL26-10	399	402	0.0085		85	0.04	2	1000	990	16	17	3	1	1.2	4.0	24	0.01
KL26-10	402	404.3	0.0188		188	0.07	4.4	2810	2020	30	61	6	1	2.1	6.5	23	0.01
KL26-10	404.3	406.4	0.012		120	0.02	2.2	1190	890	15	32	4	1	1.7	5.6	24	0.01
KL26-10	406.4	407.9	0.101		1010	0.64	51	91500	55300	560	5	0.01	1	66	27.5	43	0.14

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL26-10	407.9	411	0.008		80	0.01	0.9	450	261	15	23	5	1	0.9	0.8	16	0.01
KL26-10	411	414	0.0203		203	0.06	14.4	16400	7900	100	68	22	1	6.8	16.0	24	0.01
KL26-10	414	417	0.0152		152	0.05	9.8	2600	2160	34	37	14	1	2.4	14.0	30	0.01
KL26-10	417	420	0.0076		76	0.04	5.9	900	1170	18	58	5	1	1.5	10.0	30	0.01
KL26-10	420	423	0.0296		296	0.3	64	17600	13000	110	362	141	1	6.7	64.0	34	0.01
KL26-10	423	426	0.0122		122	0.03	8.9	1120	2020	26	87	20	1	1.5	9.2	25	0.01
KL26-10	426	429	0.0072		72	0.06	6.6	2250	2590	35	64	9	1	2.2	12.5	25	0.01
KL26-10	429	432	0.0148		148	0.04	6.3	1870	3040	33	73	9	1	2.1	15.7	31	0.01
KL26-10	432	434.3	0.0089		89	0.03	4.8	1120	2100	26	75	10	1	1.8	9.0	29	0.01
KL26-10	434.3	437.3	0.015		150	0.07	8.5	8500	5800	100	46	9	1	5.5	14.8	28	0.01
KL26-10	437.3	438.8	0.0109		109	0.04	4.1	680	1430	40	37	7	1	1.5	8.3	35	0.01
KL26-10	438.8	441	0.041		410	0.16	41	10300	6600	120	120	114	1	3.7	25.0	37	0.01
KL26-10	441	444.1	0.0112		112	0.07	5.5	1330	1920	61	33	18	1	2.7	9.0	27	0.01
KL26-10	444.1	450	0.019		190	0.1	20.8	4510	2700	67	64	49	1	3.3	14.8	30	0.01
KL26-11	0	2.4	0.0087		87	0.01	0.6	650	380	5	4	0.01	1	4	1.5	22	0.01
KL26-11	2.4	3.7	0.0023		23	0.01	1.2	345	393	2	1	0.01	1	2.1	2.0	14	0.01
KL26-11	3.7	5.7	0.0019		19	0.01	0.1	329	339	1	1	0.01	1	0.8	1.8	13	0.01
KL26-11	5.7	8.7	0.0038		38	0.01	0.1	700	470	1	1	0.01	1	0.7	2.6	15	0.01
KL26-11	8.7	11.3	0.0052		52	0.01	0.1	303	211	1	1	0.01	1	0.6	1.4	14	0.01
KL26-11	11.3	13.9	0.0009		9	0.02	0.1	480	274	1	1	0.01	1	0.5	1.6	12	0.01
KL26-11	13.9	15.7	0.0038		38	0.01	0.9	399	500	6	1	0.01	1	1.1	2.1	13	0.01
KL26-11	15.7	17.7	0.67		6700	0.24	1.1	345	88	250	123	0.01	1	5.4	4.7	228	0.01
KL26-11	17.7	19.8	0.0007		7	0.01	0.1	269	267	2	1	0.01	1	0.6	1.3	15	0.01
KL26-11	19.8	21.4	0.0026		26	0.01	0.1	130	115	2	2	0.01	1	0.5	1.0	15	0.01
KL26-11	21.4	24.2	0.0016		16	0.01	0.1	138	113	1	1	0.01	1	0.4	0.7	10	0.01
KL26-11	24.2	26.4	0.0042		42	0.01	0.6	133	180	2	3	0.01	1	0.6	1.2	10	0.01
KL26-11	26.4	29.4	0.0029		29	0.01	0.1	215	234	2	1	0.01	1	0.5	0.9	13	0.01
KL26-11	29.4	32.1	0.0018		18	0.01	0.8	570	420	5	1	0.01	1	0.9	2.9	10	0.01
KL26-11	32.1	34.2	0.0028		28	0.01	0.1	202	184	2	1	0.01	1	0.6	2.8	12	0.01
KL26-11	34.2	36	0.0023		23	0.01	0.7	170	136	2	1	0.01	1	0.4	1.7	10	0.01
KL26-11	36	38.1	0.002		20	0.01	4.2	3150	4490	3	1	0.01	1	8.7	4.5	9	0.01
KL26-11	38.1	41	0.0022		22	0.01	0.8	290	790	2	1	0.01	1	2	2.8	9	0.01
KL26-11	41	44	0.0012		12	0.01	0.1	410	560	2	2	0.01	1	0.8	1.5	12	0.01
KL26-11	44	46.6	0.0068		68	0.01	1.3	960	1140	3	1	0.01	1	1.6	1.4	8	0.01
KL26-11	46.6	48.8	0.0049		49	0.01	7.1	530	4020	10	1	0.01	1	8.9	2.6	8	0.01
KL26-11	48.8	51.5	0.0055		55	0.01	0.9	450	600	4	3	0.01	1	2.6	1.8	23	0.01
KL26-11	51.5	53.6	0.0075		75	0.01	3.7	348	3660	11	3	0.01	1	6.8	2.9	15	0.01
KL26-11	53.6	55.2	0.0033		33	0.01	1.4	235	1030	8	3	0.01	1	2.1	1.7	12	0.01
KL26-11	55.2	58.1	0.0081		81	0.01	15.1	1550	16400	58	3	0.01	1	30	11.0	12	0.01
KL26-11	58.1	60.4	0.002		20	0.01	1	560	360	6	2	0.01	1	0.9	1.6	8	0.01
KL26-11	60.4	62.7	0.0063		63	0.01	1.5	550	960	9	4	0.01	1	1.2	2.9	11	0.01
KL26-11	62.7	65.4	0.0056		56	0.01	0.6	175	610	3	2	0.01	1	0.9	0.8	12	0.01
KL26-11	65.4	67.9	0.0116		116	0.02	1	640	920	2	3	0.01	1	1.3	1.7	12	0.01
KL26-11	67.9	70.2	0.0038		38	0.01	0.1	177	342	3	2	1	1	0.5	0.9	11	0.01
KL26-11	70.2	72.9	0.0021		21	0.02	0.1	365	256	4	2	1	1	0.5	1.5	12	0.01
KL26-11	72.9	75.8	0.0035		35	0.01	0.8	770	620	5	2	0.01	1	1.7	1.4	11	0.01
KL26-11	75.8	78.7	0.0021		21	0.01	0.9	460	315	9	3	1	1	0.7	2.1	10	0.01
KL26-11	78.7	81.2	0.0016		16	0.01	0.1	410	356	4	3	0.01	1	0.8	1.2	11	0.01
KL26-11	81.2	83.6	0.0194		194	0.07	1.2	870	1190	5	3	0.01	1	1.1	1.8	12	0.01
KL26-11	83.6	86.2	0.0039		39	0.01	2.5	2970	2350	16	2	0.01	1	4.8	1.7	12	0.01
KL26-11	86.2	89.2	0.0019		19	0.01	0.1	201	266	9	4	0.01	1	0.5	1.1	11	0.01
KL26-11	89.2	91.2	0.002		20	0.01	0.1	273	270	7	2	0.01	1	0.8	1.7	11	0.01
KL26-11	91.2	94.2	0.0021		21	0.01	0.6	306	228	8	3	0.01	1	0.9	1.6	11	0.01
KL26-11	94.2	97.2	0.0073		73	0.01	1.3	397	373	41	3	0.01	1	1.2	4.3	14	0.01
KL26-11	97.2	100.2	0.0184		184	0.01	2.2	1640	880	26	3	0.01	1	1.8	8.0	28	0.01
KL26-11	100.2	103.2	0.0051		51	0.01	1.8	790	1010	13	3	0.01	1	1.2	2.3	17	0.01
KL26-11	103.2	106.2	0.0133		133	0.01	0.5	238	295	14	86	1	1	1.2	1.5	23	0.01
KL26-11	106.2	109.2	0.004		40	0.01	0.6	113	171	17	9	0.01	1	0.6	1.3	27	0.01
KL26-11	109.2	112.2	0.0128		128	0.03	1.6	1220	1330	26	33	2	1	2.6	3.0	32	0.01
KL26-11	112.2	115.2	0.008		80	0.01	0.1	286	236	13	9	8	1	0.7	5.9	48	0.01
KL26-11	115.2	118.2	0.0204		204	0.01	1.2	410	800	20	5	2	1	1.3	5.8	21	0.01
KL26-11	118.2	121.2	0.0085		85	0.04	2.1	510	440	23	4	0.01	1	2.5	4.8	24	0.01
KL26-11	121.2	124.2	0.0036		36	0.01	2.1	138	398	23	4	0.01	1	1.5	7.6	27	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL26-11	124.2	127.2	0.0047		47	0.01	2.7	1020	1000	18	8	4	1	1.6	13.8	30	0.01
KL26-11	127.2	130.2	0.0012		12	0.01	0.8	286	242	19	4	2	1	0.6	12.1	28	0.01
KL26-11	130.2	133.2	0.0048		48	0.01	0.1	140	265	21	2	0.01	1	1.2	4.9	31	0.01
KL26-11	133.2	136.2	0.0171		171	0.02	0.6	92	166	14	9	2	1	1.4	3.0	12	0.01
KL26-11	136.2	139.2	0.0157		157	0.01	1.2	153	360	11	4	0.01	1	1.6	4.4	16	0.01
KL26-11	139.2	142.2	0.0037		37	0.01	1	146	700	13	3	3	1	1.9	2.9	17	0.01
KL26-11	142.2	143.8	0.0005		5	0.01	0.1	127	185	8	2	0.01	1	0.6	1.9	10	0.01
KL26-11	143.8	146.7	0.0035		35	0.01	0.7	170	266	10	3	0.01	1	0.7	2.8	18	0.01
KL26-11	146.7	149.7	0.0007		7	0.01	0.1	55	135	9	2	0.01	1	0.5	2.0	15	0.01
KL26-11	149.7	151.2	0.023		230	0.1	1.3	219	204	29	3	6	1	0.7	3.4	24	0.01
KL26-11	151.2	154.2	0.0101		101	0.01	1.2	224	160	23	69	27	1	2.5	3.1	27	0.01
KL26-11	154.2	155.7	0.0148		148	0.01	0.1	68	80	6	18	0.01	2	0.9	2.0	34	0.01
KL26-11	155.7	157.2	0.0041		41	0.03	0.1	203	336	17	27	0.01	2	1	4.7	77	0.01
KL26-11	157.2	158.8	0.0129		129	0.03	0.1	105	161	9	26	1	3	1	3.6	152	0.01
KL26-11	158.8	161.4	0.0221		221	0.02	0.1	74	97	19	11	4	7	0.8	8.4	112	0.01
KL26-11	161.4	164	0.056		560	0.05	2.6	930	1100	60	14	20	11	4.8	41.8	32	0.01
KL26-11	164	165.1	0.083		830	0.04	3	500	840	160	118	1	3	18.3	8.0	83	0.01
KL26-11	165.1	167.8	0.245		2450	0.23	3	3890	530	430	210	4	12	5	11.0	68	0.01
KL26-11	167.8	169.2	0.9		9000	0.59	18	1750	1400	260	620	12	25	8	25.3	125	0.01
KL26-11	169.2	172.2	0.12		1200	0.41	27.8	15900	11500	350	55	2	5	101	15.0	87	0.38
KL26-11	172.2	175.2	0.078		780	0.09	6.4	1560	1410	45	103	4	3	6.6	6.9	92	0.01
KL26-11	175.2	178.2	0.0353		353	0.04	1.8	287	580	21	128	2	2	3.2	3.8	102	0.01
KL26-11	178.2	181.2	0.113		1130	0.2	28.5	11200	23900	300	60	20	2	44	14.5	63	0.12
KL26-11	181.2	184.2	0.419		4190	0.09	7.8	1710	1390	30	118	7	22	2.3	12.0	50	0.01
KL26-11	184.2	187.2	0.458		4580	0.12	7.3	1550	1320	48	335	13	12	2.6	7.3	40	0.01
KL26-11	187.2	190	0.059		590	0.45	14.3	1760	1770	84	385	144	6	2.4	11.8	30	0.01
KL26-11	190	193.2	0.0128		128	0.06	10	2500	3760	15	65	8	1	3.8	12.9	27	0.01
KL26-11	193.2	196.2	0.0183		183	0.08	12	3260	2660	25	45	2	1	4.1	11.5	25	0.01
KL26-11	196.2	199.2	0.0253		253	0.1	23	12800	7700	22	60	36	1	2.8	20.0	27	0.01
KL26-11	199.2	202.2	0.0166		166	0.05	10.8	3550	5500	10	26	3	1	3.6	18.0	25	0.01
KL26-11	202.2	205.2	0.013		130	0.02	7.8	3060	3490	12	18	1	4	3.4	11.0	28	0.01
KL26-11	205.2	208.2	0.0073		73	0.03	3.2	860	2600	21	10	1	1	3.2	10.3	25	0.01
KL26-11	208.2	211.2	0.0081		81	0.04	4.6	1490	4290	17	26	1	1	4.3	8.5	25	0.01
KL26-11	211.2	214.2	0.0157		157	0.03	4.4	3560	3490	64	18	0.01	1	4	11.3	30	0.01
KL26-11	214.2	217.2	0.0154		154	0.03	2.7	1390	2450	10	25	1	1	2.9	6.7	32	0.01
KL26-11	217.2	220.2	0.0192		192	0.12	16.2	6800	7900	12	49	2	1	5.3	21.3	35	0.01
KL26-11	220.2	223.2	0.0072		72	0.03	6.7	5100	5400	18	13	0.01	1	5.9	17.0	30	0.01
KL26-11	223.2	226.2	0.0193		193	0.52	15.3	4520	4980	46	50	40	2	5	55.0	38	0.01
KL26-11	226.2	229.2	0.0055		55	0.01	3.9	900	2270	12	27	7	1	2.9	7.8	20	0.01
KL26-11	229.2	232.2	0.0102		102	0.01	1.7	720	1430	8	13	2	1	1.5	6.3	18	0.01
KL26-11	232.2	233.8	0.0285		285	0.04	2.5	3850	3200	11	30	1	1	1.8	9.5	21	0.1
KL26-11	233.8	236.8	0.0116		116	0.05	1.4	1780	2990	10	66	1	1	1.7	21.8	19	0.01
KL26-11	236.8	239.8	0.07		700	0.16	3.5	4870	3390	21	37	11	1	2.5	21.5	20	0.01
KL26-11	239.8	242.5	0.0179		179	0.05	0.9	2550	1600	14	56	1	1	1.3	9.0	20	0.01
KL26-11	242.5	244.1	0.112		1120	0.77	2.3	6500	1660	29	54	23	1	2.5	27.9	27	0.01
KL26-11	244.1	245.7	0.045		450	0.2	3.6	4200	3500	17	110	16	2	1.7	17.1	22	0.01
KL26-11	245.7	248.7	0.178		1780	0.29	4.1	10600	3700	7	74	44	4	5.2	32.5	22	0.01
KL26-11	248.7	251.6	0.098		980	0.11	2.2	2070	1670	8	83	6	3	0.6	13.0	19	0.01
KL26-11	251.6	254.6	0.201		2010	0.31	2	1840	27	7	3	8	4	0.01	8.0	21	0.01
KL26-11	254.6	256.2	0.045		450	0.1	1	820	120	12	8	2	2	0.4	3.8	16	0.01
KL26-11	256.2	259.2	0.41		4100	0.45	1.8	5700	94	9	12	7	7	0.7	21.2	22	0.01
KL26-11	259.2	262.2	0.15		1500	0.12	1.8	680	93	10	3	5	4	0.01	7.9	24	0.01
KL26-11	262.2	265.2	0.075		750	0.13	1.7	3200	710	10	12	8	4	0.01	26.5	28	0.01
KL26-11	265.2	268.1	0.14		1400	0.99	17.3	1580	410	5	3	570	5	0.01	197.0	24	0.01
KL26-11	268.1	269.6	0.078		780	0.17	1.6	1480	81	12	7	3	3	0.4	5.5	36	0.01
KL26-11	269.6	271.7	0.39		3900	0.25	5.4	2980	125	13	12	35	9	0.9	11.0	27	0.01
KL26-11	271.7	274.2	0.23		2300	0.22	4.5	2700	36	30	4	5	5	0.5	6.5	21	0.01
KL26-11	274.2	277.2	0.31		3100	0.44	6.4	6900	59	12	3	40	5	1.8	9.8	33	0.01
KL26-11	277.2	280.2	0.89		8900	1.72	4	2220	283	17	43	70	8	0.7	24.0	30	0.01
KL26-11	280.2	283.2	0.57		5700	1.02	2	500	45	10	168	10	4	0.3	16.5	37	0.01
KL26-11	283.2	286.2	0.21		2100	0.27	1.9	1150	368	4	205	17	2	0.4	25.8	34	0.01
KL26-11	286.2	289.2	0.154		1540	0.35	1	660	77	11	460	9	1	0.3	5.8	39	0.01
KL26-11	289.2	292.2	0.192		1920	0.73	1	168	49	11	73	75	1	0.2	10.3	46	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL26-11	292.2	295.2	0.95	9500	1.27	3.1	7900	91	24	110	46	15	0.2	87.0	20	0.01
KL26-11	295.2	296.8	0.81	8100	1.05	3.5	390	162	5	382	90	8	0.6	39.5	18	0.01
KL26-11	296.8	299.8	1.92	19200	1.08	5.2	16600	81	2	158	67	24	0.3	70.0	18	0.01
KL26-11	299.8	302.8	0.44	4400	1.82	1.8	1130	75	3	125	150	6	0.4	47.5	19	0.01
KL26-11	302.8	305.7	0.53	5300	0.31	1.7	2980	92	3	123	2	9	0.3	10.0	25	0.01
KL26-11	305.7	308.7	0.098	980	0.35	1.2	185	78	22	19	30	2	0.01	4.5	31	0.01
KL26-11	308.7	311.7	0.095	950	0.07	0.8	490	49	20	374	6	2	0.3	4.3	41	0.01
KL26-11	311.7	314.7	0.63	6300	0.4	1.5	1000	34	1	22	0.01	10	0.01	8.8	23	0.01
KL26-11	314.7	317.8	0.102	1020	0.21	0.9	450	45	3	67	5	5	0.4	4.0	14	0.01
KL26-11	317.8	320.8	0.23	2300	0.11	1	300	23	3	34	2	8	0.4	4.8	17	0.01
KL26-11	320.8	323.8	0.37	3700	0.15	1.2	286	97	17	9	1	7	0.01	8.0	29	0.01
KL26-11	323.8	326.8	0.8	8000	0.29	4.2	1440	137	10	4	5	11	0.3	9.5	24	0.01
KL26-11	326.8	329.8	0.86	8600	0.25	6.3	28400	186	6	3	11	100	1.1	23.5	27	0.01
KL26-11	329.8	332.6	0.73	7300	0.77	8.9	8100	1300	2	3	14	35	0.9	12.0	23	0.01
KL26-11	332.6	334.2	0.0336	336	0.29	16.8	10000	17200	11	7	3	1	4.5	20.5	24	0.01
KL26-11	334.2	337.2	0.2	2000	0.25	6.4	9800	2500	6	3	17	10	1	10.0	26	0.01
KL26-11	337.2	338.8	0.185	1850	0.23	2.4	5000	50	5	3	16	20	0.4	5.5	24	0.01
KL26-11	338.8	340.2	1.03	10300	0.88	6.1	7200	87	4	8	26	74	4	16.0	20	0.01
KL26-11	340.2	343.2	1.94	19400	1.65	2.4	380	10	1	11	1	42	0.01	15.5	22	0.01
KL26-11	343.2	346.2	0.24	2400	0.49	0.7	241	31	1	7	1	25	0.01	5.8	28	0.01
KL26-11	346.2	349.2	0.34	3400	0.35	1	130	15	0.01	6	1	15	0.01	7.5	19	0.01
KL26-11	349.2	352.2	1.04	10400	1.76	8.6	115	50	1	4	4	16	0.01	11.3	32	0.01
KL26-11	352.2	355.2	0.84	8400	1.48	3.7	136	69	2	16	7	15	0.01	12.5	41	0.01
KL26-11	355.2	358.2	0.81	8100	0.5	1.3	225	59	4	9	3	22	0.01	14.5	35	0.01
KL26-11	358.2	361.2	2.7	27000	0.83	3	158	22	0.01	5	4	54	0.01	36.0	56	0.01
KL26-11	361.2	364.2	2.49	24900	1.47	4.4	157	37	6	6	5	29	0.2	21.0	52	0.15
KL26-11	364.2	367.2	1.46	14600	1.95	2.6	161	56	10	110	7	26	0.5	10.0	32	0.01
KL26-11	367.2	370.2	1.52	15200	4.31	3	113	14	0.01	9	12	25	0.2	17.3	62	0.01
KL26-11	370.2	373.2	2	20000	1.53	2.5	146	8	1	8	2	18	0.01	10.5	75	0.01
KL26-11	373.2	375.8	0.94	9400	1.79	1.9	41	10	3	16	1	11	0.01	6.5	234	0.01
KL26-11	375.8	377.4	1.05	10500	3.49	2.3	59	18	42	26	4	8	0.3	10.0	224	0.01
KL26-11	377.4	380.6	0.53	5300	0.4	1.8	91	34	10	720	6	11	0.5	6.0	89	0.01
KL26-11	380.6	382.2	0.67	6700	0.43	3.1	143	29	2	3500	2	10	0.3	11.0	117	0.01
KL26-11	382.2	385.2	0.6	6000	0.4	1.7	127	33	6	1590	1	11	0.3	7.9	173	0.01
KL26-11	385.2	388.2	0.47	4700	0.36	1.3	138	54	3	32	1	12	0.2	6.5	97	0.01
KL26-11	388.2	389.8	0.76	7600	0.53	1.8	114	38	1	28	1	12	0.2	4.5	87	0.01
KL26-11	389.8	392.8	0.62	6200	0.56	1.8	139	14	1	130	1	12	0.01	6.0	92	0.01
KL26-11	392.8	395.8	0.6	6000	1.3	1.5	94	32	2	33	1	10	0.2	6.0	105	0.01
KL26-11	395.8	398.8	0.91	9100	0.57	1.6	79	12	1	38	0.01	12	0.01	5.2	68	0.01
KL26-11	398.8	401.8	0.83	8300	0.96	1.3	108	24	2	18	0.01	15	0.01	6.8	118	0.01
KL26-11	401.8	404.8	0.93	9300	0.59	2	140	37	1	356	1	15	0.01	6.0	94	0.01
KL26-11	404.8	407.8	0.81	8100	0.76	1.7	101	22	2	91	1	10	0.01	5.5	88	0.01
KL26-11	407.8	409.2	0.94	9400	0.89	1.8	128	20	1	103	3	13	0.01	8.0	80	0.01
KL26-11	409.2	412.2	1.24	12400	0.85	2	107	14	0.01	31	3	14	0.2	8.5	78	0.01
KL26-11	412.2	415.2	0.88	8800	0.53	1.7	90	6	0.01	18	0.01	21	0.01	4.0	64	0.01
KL26-11	415.2	418.2	0.7	7000	0.64	1.6	107	12	0.01	9	0.01	11	0.01	3.0	65	0.01
KL26-11	418.2	421.2	0.85	8500	0.61	1.4	140	20	0.01	18	0.01	11	0.01	4.3	95	0.01
KL26-11	421.2	424.2	0.47	4700	0.36	1.2	77	52	0.01	41	0.01	11	0.01	4.0	71	0.01
KL26-11	424.2	427.1	0.46	4600	0.4	0.9	130	7	0.01	31	0.01	10	0.01	3.8	85	0.01
KL26-11	427.1	430.2	0.6	6000	0.52	1.2	53	8	0.01	25	0.01	12	0.01	5.8	96	0.01
KL26-11	430.2	433.2	0.92	9200	0.87	1.8	86	18	1	74	1	10	0.01	5.5	111	0.01
KL26-11	433.2	436.2	0.58	5800	0.41	1.7	129	55	1	87	0.01	10	0.01	6.3	78	0.01
KL26-11	436.2	439.2	0.39	3900	0.2	1	103	42	21	57	4	14	1.7	15.0	88	0.01
KL26-11	439.2	442.2	0.74	7400	0.49	1.6	79	16	1	27	1	9	0.01	5.5	89	0.01
KL26-11	442.2	445.2	0.41	4100	0.35	1.4	104	13	1	57	1	7	0.01	4.3	70	0.01
KL26-11	445.2	448.2	0.5	5000	0.33	1.3	75	13	0.01	26	0.01	9	0.01	5.0	71	0.01
KL26-11	448.2	451.2	0.62	6200	0.47	1.7	114	21	0.01	50	1	11	0.01	6.3	80	0.01
KL28-01	0	2.6	0.0028	28	0.01	0.1	63	34	5	1	0.01	3	0.3	1.1	17	0.01
KL28-01	2.6	5.6	0.0117	117	0.01	2.4	1130	1220	9	1	0.01	2	4.7	3.1	18	0.01
KL28-01	5.6	8.6	0.0058	58	0.01	0.1	86	104	8	2	0.01	3	0.6	1.0	21	0.01
KL28-01	8.6	11.6	0.0028	28	0.04	0.1	37	27	6	1	0.01	2	0.2	1.2	23	0.01
KL28-01	11.6	14.6	0.0029	29	0.01	0.1	45	34	5	2	0.01	3	0.01	1.3	26	0.01
KL28-01	14.6	17.6	0.0032	32	0.01	0.1	50	31	4	1	0.01	1	0.2	1.4	19	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL28-01	17.6	20.6	0.002		20	0.01	0.1	49	32	5	1	0.01	1	0.3	2.7	16	0.01
KL28-01	20.6	23.6	0.0018		18	0.01	0.1	73	67	7	1	0.01	1	0.01	1.6	26	0.01
KL28-01	23.6	26.6	0.0018		18	0.01	0.1	63	24	8	1	0.01	1	0.01	1.3	24	0.01
KL28-01	26.6	29.6	0.0034		34	0.01	0.1	64	40	4	1	0.01	1	0.2	1.4	28	0.01
KL28-01	29.6	32.6	0.0046		46	0.01	0.1	61	46	5	1	0.01	1	0.01	1.5	25	0.01
KL28-01	32.6	35.6	0.0021		21	0.02	0.1	73	48	7	1	0.01	1	0.3	2.5	24	0.01
KL28-01	35.6	38.6	0.0215		215	0.14	1.8	191	169	25	1	3	3	3.5	4.1	56	0.01
KL28-01	38.6	40.7	0.0399		399	0.04	0.7	57	94	13	20	2	2	1.6	3.1	138	0.01
KL28-01	40.7	43.1	0.042		420	0.01	3.3	100	600	26	8	18	7	2.3	8.8	124	0.01
KL28-01	43.1	48.6	0.0431		431	0.2	55.8	4500	8900	110	18	76	3	24	42.0	41	0.01
KL28-01	48.6	51.6	0.054		540	0.25	11.8	380	2980	60	17	12	3	10.4	7.4	41	0.01
KL28-01	51.6	54.6	0.0194		194	0.05	6.1	530	3740	14	15	4	1	3.9	2.3	41	0.01
KL28-01	54.6	56.6	0.0203		203	0.07	3.3	307	1490	21	10	3	1	5.4	1.7	43	0.01
KL28-01	56.6	58.6	0.017		170	0.11	2.8	342	1740	10	14	2	1	2.5	0.0	36	0.01
KL28-01	58.6	61.3	0.0107		107	0.04	1.4	124	710	15	14	0.01	2	4.5	0.0	22	0.01
KL28-01	61.3	64.4	0.0147		147	0.03	0.1	103	187	12	12	0.01	1	2.4	0.0	30	0.01
KL28-01	64.4	67.4	0.0041		41	0.02	0.9	87	217	6	5	0.01	1	1.6	0.7	9	0.01
KL28-01	67.4	70.1	0.0059		59	0.01	0.1	183	98	6	5	0.01	1	1	0.0	8	0.01
KL28-01	70.1	73.1	0.0051		51	0.01	0.1	150	251	8	2	0.01	1	1.2	0.0	6	0.01
KL28-01	73.1	75.6	0.015		150	0.01	2	327	720	13	5	0.01	1	3	0.0	9	0.01
KL28-01	75.6	78.6	0.0042		42	0.01	1	90	620	23	4	0.01	1	3.1	0.0	7	0.01
KL28-01	78.6	81.6	0.0047		47	0.01	2.1	87	201	24	1	0.01	1	5.1	0.6	12	0.01
KL28-01	81.6	84.6	0.081		810	0.16	184	12400	19700	54	10	3	2	245	22.0	58	0.01
KL28-01	84.6	86.3	0.0173		173	0.04	44.3	2370	1750	33	2	2	1	15.5	18.0	27	0.01
KL28-01	86.3	89.3	0.069		690	0.07	124	14000	11800	160	1	3	2	52	42.0	24	0.01
KL28-01	89.3	92.3	0.0063		63	0.04	10.1	740	710	13	5	0.01	2	3.7	4.0	15	0.01
KL28-01	92.3	94.9	0.0073		73	0.05	14.5	520	1670	15	6	0.01	2	6.8	4.7	21	0.01
KL28-01	94.9	97.1	0.0019		19	0.01	2.4	210	417	2	3	0.01	1	2.2	1.9	22	0.01
KL28-01	97.1	100.1	0.0047		47	0.02	5.3	710	1180	10	3	0.01	2	4.2	4.5	21	0.01
KL28-01	100.1	103.1	0.0061		61	0.01	4.5	234	1460	10	2	1	2	3.5	3.7	21	0.01
KL28-01	103.1	106.1	0.0043		43	0.07	3.4	240	840	9	1	1	2	2.9	3.9	22	0.01
KL28-01	106.1	109.1	0.0024		24	0.01	1.6	89	324	2	1	1	1	1.1	1.4	24	0.01
KL28-01	109.1	112.1	0.0096		96	0.01	2.2	210	309	12	1	1	2	1.5	1.3	26	0.01
KL28-01	112.1	114.4	0.0036		36	0.01	0.8	67	187	5	1	1	2	1.8	1.0	22	0.01
KL28-01	114.4	116.8	0.004		40	0.01	2	329	540	8	1	1	2	1	1.2	23	0.01
KL28-01	116.8	119.6	0.002		20	0.01	0.9	80	101	3	1	0.01	3	0.9	0.7	23	0.01
KL28-01	119.6	123.1	0.003		30	0.01	1.5	130	490	4	1	0.01	3	0.6	0.9	23	0.01
KL28-01	123.1	125.4	0.0008		8	0.02	0.8	44	160	6	1	0.01	2	1.5	1.1	25	0.01
KL28-01	125.4	127.9	0.0028		28	0.01	0.9	110	300	5	1	0.01	2	1.8	0.9	26	0.01
KL28-01	127.9	130.9	0.0034		34	0.01	0.7	45	120	4	1	1	2	2	0.7	29	0.01
KL28-01	130.9	133.1	0.004		40	0.01	2.2	412	1010	6	1	1	1	2.6	0.9	21	0.01
KL28-01	133.1	136.1	0.002		20	0.01	2.4	251	490	5	9	0.01	1	1.1	1.0	14	0.01
KL28-01	136.1	139.1	0.002		20	0.01	2.4	470	910	6	6	0.01	1	1.9	1.6	10	0.01
KL28-01	139.1	141.5	0.0022		22	0.01	2.3	406	950	5	4	0.01	2	1.9	1.7	8	0.01
KL28-01	141.5	144.4	0.0033		33	0.01	1.9	930	860	7	6	0.01	1	2.9	1.6	13	0.01
KL28-01	144.4	146.6	0.0016		16	0.01	0.9	332	376	3	5	0.01	1	0.8	0.9	13	0.01
KL28-01	146.6	149.7	0.0029		29	0.02	4.3	1280	3410	4	8	0.01	1	4.5	3.0	13	0.01
KL28-01	149.7	152.6	0.003		30	0.01	2.1	840	810	3	7	0.01	1	1.2	1.7	10	0.01
KL28-01	152.6	155.2	0.0031		31	0.01	3.8	1000	1310	4	8	4	1	1.3	3.4	8	0.01
KL28-01	155.2	158.2	0.0045		45	0.06	11.5	1530	2630	19	12	5	2	3.3	7.9	14	0.01
KL28-01	158.2	161.2	0.0023		23	0.02	4.3	1460	100	7	3	0.01	1	2.1	4.0	12	0.01
KL28-01	161.2	164.1	0.0034		34	0.01	2.1	490	1040	3	4	0.01	1	2.1	4.5	19	0.01
KL28-01	164.1	166.1	0.002		20	0.01	0.9	301	430	2	4	0.01	1	1.4	3.4	15	0.01
KL28-01	166.1	167.7	0.0018		18	0.01	1.7	214	286	3	3	0.01	1	0.8	2.7	15	0.01
KL28-01	167.7	170.6	0.0017		17	0.02	1	160	199	3	4	0.01	1	0.6	2.1	15	0.01
KL28-01	170.6	173.5	0.0019		19	0.01	0.8	146	217	4	3	0.01	1	0.7	1.2	12	0.01
KL28-01	173.5	176.6	0.0024		24	0.01	0.8	151	201	6	4	0.01	1	0.9	2.0	16	0.01
KL28-01	176.6	179.6	0.0057		57	0.01	1.6	580	610	5	16	0.01	3	1.7	2.5	13	0.01
KL28-01	179.6	182.6	0.0085		85	0.05	10.2	8400	5400	19	15	0.01	3	8	8.0	12	0.01
KL28-01	182.6	185.6	0.0072		72	0.07	7.5	7100	3700	11	9	1	4	6.5	9.0	10	0.01
KL28-01	185.6	188.6	0.0146		146	0.11	5.7	2770	1910	49	43	2	4	7.5	6.8	16	0.01
KL28-01	188.6	191.6	0.0071		71	0.11	4.3	990	1910	40	23	2	5	5.5	4.3	28	0.01
KL28-01	191.6	194.4	0.0259		259	0.21	36	48000	23800	38	16	8	5	32	40.3	13	0.43

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL28-01	194.4	197.6	0.0142	142	0.29	14	11300	6700	46	25	4	3	10.2	8.7	13	0.01
KL28-01	197.6	200.1	0.0057	57	0.12	3.7	1520	1650	25	14	3	4	2.6	3.3	11	0.01
KL28-01	200.1	203.6	0.0044	44	0.15	1.5	1060	480	21	8	2	3	1.2	2.3	11	0.01
KL28-01	203.6	206.4	0.055	550	0.17	4.1	1130	600	17	10	6	4	0.9	5.5	10	0.01
KL28-01	206.4	209.4	0.058	580	0.38	7.8	3960	3800	72	36	31	6	4.4	15.0	16	0.36
KL28-01	209.4	212.1	0.18	1800	0.82	7.6	1200	740	730	11	4	10	8.1	9.0	17	0.67
KL28-01	212.1	215.2	0.47	4700	1.26	13.7	12200	780	340	60	64	12	2.3	16.5	41	2.65
KL28-01	215.2	218.4	0.49	4900	4	32.7	23300	1740	970	510	210	18	22	24.5	170	2.88
KL28-01	218.4	221.4	0.161	1610	1.32	8.4	1030	315	250	1415	20	14	6.2	6.0	127	0.15
KL28-01	221.4	223.1	0.198	1980	1.16	7.9	940	600	260	1080	5	11	4.5	6.3	154	0.47
KL28-01	223.1	226.1	0.84	8400	1.89	60	14000	3400	65	250	344	25	7.6	15.3	40	0.13
KL28-01	226.1	229.1	0.69	6900	1.01	36	3650	2690	27	15	66	12	1	14.0	23	0.01
KL28-01	229.1	232.1	0.52	5200	0.75	45	10100	22900	28	460	57	13	1.7	80.5	20	0.01
KL28-01	232.1	235.1	0.66	6600	1.35	15.6	870	1660	18	700	12	12	1.3	8.5	28	0.01
KL28-01	235.1	238.1	1.1	11000	2.04	18.6	820	1430	24	270	3	22	1	12.3	23	0.01
KL28-01	238.1	241	0.65	6500	0.67	14.4	6000	1110	48	78	34	31	2.2	26.7	21	0.01
KL28-01	241	244.1	1.04	10400	1.19	10.3	289	91	25	56	21	26	1.8	12.8	41	0.01
KL28-01	244.1	247.1	1.05	10500	0.9	8.2	277	38	25	94	35	50	2.2	16.5	43	0.01
KL28-01	247.1	250.1	0.99	9900	0.94	7.8	267	36	28	470	44	25	2	13.5	73	0.01
KL28-01	250.1	252.4	0.57	5700	0.82	4.3	302	55	55	770	28	8	4	17.3	74	0.1
KL28-01	252.4	254.6	0.59	5900	0.88	4.2	336	39	57	271	20	6	1.9	11.3	36	0.01
KL28-01	254.6	257.6	3.27	32700	1.98	7.6	730	650	15	460	1	154	1.4	16.0	99	0.01
KL28-01	257.6	260.6	1.28	12800	3.2	15.9	660	107	2300	83	65	34	83	11.5	137	0.01
KL28-01	260.6	263.6	2.05	20500	2.85	22.1	1020	67	2000	8	67	20	76	15.0	175	0.31
KL28-01	263.6	266.6	1.64	16400	1.63	5.9	383	26	31	162	1	87	2.8	11.5	36	0.01
KL28-01	266.6	269.6	3.43	34300	3.24	12.6	264	40	13	58	0.01	118	1.8	18.0	24	0.01
KL28-01	269.6	272.6	1.75	17500	1.21	4.7	131	16	4	62	0.01	133	0.7	13.0	36	0.01
KL28-01	272.6	275.6	1.8	18000	1.3	4.4	112	10	2	410	0.01	99	0.2	12.0	74	0.01
KL28-01	275.6	278.6	3.95	39500	4.1	7.3	450	34	21	2270	0.01	127	0.6	31.0	47	0.01
KL28-01	278.6	281.6	2.1	21000	1.23	3.5	117	8	2	4550	0.01	68	0.01	21.0	38	0.01
KL28-01	281.6	284.6	3.54	35400	2.01	4.8	154	8	0.01	74	0.01	73	0.01	27.0	36	0.01
KL28-01	284.6	287.6	2.42	24200	4.23	4	104	12	10	181	0.01	54	0.3	14.4	60	0.01
KL28-01	287.6	290.6	1.46	14600	1.33	2.1	109	12	1	95	0.01	60	0.01	11.4	34	0.01
KL28-01	290.6	293.6	4.83	48300	3.67	5.5	192	10	3	970	0.01	90	0.01	23.2	63	0.01
KL28-01	293.6	296.6	5.38	53800	4.12	7.5	710	430	730	930	0.01	83	13.5	28.2	101	0.11
KL28-01	296.6	299.6	2.69	26900	1.62	2.5	282	73	23	1110	0.01	45	0.9	25.0	140	0.01
KL28-01	299.6	301.5	3.74	37400	1.86	2.9	225	31	9	1080	0.01	58	0.9	22.0	80	0.01
KL28-01	301.5	304.5	1.75	17500	1.41	2.1	690	60	34	1690	0.01	51	1.1	28.3	125	0.01
KL28-01	304.5	307.1	1.24	12400	0.67	2.5	910	320	1410	900	0.01	28	45	10.3	72	0.24
KL28-01	307.1	310.1	3.65	36500	2.19	3.2	450	85	55	4450	0.01	40	2.1	21.5	112	0.01
KL28-01	310.1	313.1	2.01	20100	1.22	2.1	410	93	22	12400	0.01	32	1.4	18.0	95	0.01
KL28-01	313.1	316.1	2.16	21600	0.89	2.2	315	76	12	1270	0.01	32	0.8	21.0	56	0.01
KL28-01	316.1	319.1	1.82	18200	0.7	2	500	161	13	1040	0.01	26	0.4	15.2	74	0.01
KL28-01	319.1	322.1	2.25	22500	0.69	1.9	377	165	24	1280	0.01	29	0.5	13.2	40	0.01
KL28-01	322.1	325.1	2.62	26200	0.65	2.1	215	179	13	1420	0.01	29	0.5	13.3	43	0.01
KL28-01	325.1	328.1	1.85	18500	1.06	2.1	460	460	87	1100	0.01	28	0.4	8.0	38	0.01
KL28-01	328.1	331.1	1.05	10500	1.15	1.5	540	560	110	730	0.01	22	1.6	8.5	44	0.22
KL28-01	331.1	334.1	1	10000	0.6	1.4	271	193	11	780	0.01	16	0.3	9.0	43	0.01
KL28-01	334.1	337.1	2.14	21400	0.7	1.9	286	202	9	1200	0.01	26	0.4	9.5	53	0.01
KL28-01	337.1	340.1	2.54	25400	0.8	2.1	750	540	110	1030	0.01	23	0.5	11.0	60	0.58
KL28-01	340.1	343.1	2.57	25700	0.78	2.7	1890	500	24	1250	0.01	28	0.3	16.0	132	0.48
KL28-01	343.1	346.1	2.66	26600	1.04	2.6	720	156	240	1880	0.01	28	0.3	14.5	113	0.52
KL28-01	346.1	347.6	2.91	29100	1.18	2.7	290	151	30	1120	0.01	39	0.5	16.0	53	0.2
KL28-01	347.6	350.1	1.79	17900	0.6	2.2	1510	580	200	1560	0.01	24	1.4	11.5	53	1.24
KL28-01	350.1	353.1	1.66	16600	0.41	2	1140	650	230	1360	0.01	27	0.9	11.5	52	1.13
KL28-01	353.1	356.1	1.6	16000	0.4	1.9	840	660	87	1770	0.01	27	0.2	13.0	64	1.13
KL28-01	356.1	359.1	3.06	30600	1.2	3	157	42	240	900	0.01	46	0.4	18.5	174	0.66
KL28-01	359.1	361.1	2.85	28500	1	2.6	83	16	20	640	0.01	77	0.01	15.0	168	0.01
KL28-01	361.1	364.1	2.93	29300	1.76	3.4	132	16	23	290	0.01	90	0.01	13.0	62	0.01
KL28-01	364.1	367.1	2.76	27600	2.71	7.2	182	16	7	310	2	48	0.01	21.5	50	0.01
KL28-01	367.1	370.1	1.93	19300	2.48	7.1	3000	420	30	90	2	33	1.3	12.8	52	0.8
KL28-01	370.1	373.1	2.51	25100	1.87	6.8	500	53	14	110	2	129	0.4	34.0	36	0.01
KL28-01	373.1	376.1	2.58	25800	1.59	7.1	161	20	13	76	7	121	0.7	43.1	37	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL28-01	376.1	379.1	2.03	20300	1.7	6.1	1100	125	62	28	10	93	1	37.7	28	0.31
KL28-01	379.1	382.1	2.44	24400	2.01	11.7	315	59	51	6	34	62	1.6	21.0	46	0.2
KL28-01	382.1	385.1	1.66	16600	0.77	7.3	369	94	390	13	9	42	2.5	19.0	42	0.45
KL28-01	385.1	388.1	1.49	14900	0.71	6	1020	110	690	14	2	54	1.8	30.7	33	1.15
KL28-01	388.1	389.6	1.38	13800	0.85	5.8	1040	163	560	10	6	36	1.9	22.4	26	1.05
KL28-01	389.6	392.6	4.29	42900	3.56	15.4	660	58	45	2	42	29	1.1	29.0	41	0.25
KL28-01	392.6	394.1	1.89	18900	1.51	11.8	1850	63	65	11	12	29	0.9	26.8	64	0.01
KL28-01	394.1	397.1	1.7	17000	1.1	12.2	3400	185	71	6	34	23	0.8	18.1	84	0.28
KL28-01	397.1	400.1	2.69	26900	1.86	15	4300	590	390	24	33	79	0.6	28.0	45	2.23
KL28-01	400.1	402.1	2.54	25400	2.41	15.4	3400	490	470	89	24	204	0.7	39.0	34	1.3
KL28-01	402.1	405	2.41	24100	3.01	16.4	930	70	37	6	12	81	1.6	18.0	28	0.01
KL28-01	405	406.6	2.51	25100	3.71	15.6	1600	183	28	4	6	47	2.5	16.5	26	0.01
KL28-01	406.6	409.1	1.58	15800	3.34	10.9	1180	210	61	8	12	72	1.2	14.7	42	0.01
KL28-01	409.1	412	2.33	23300	3.75	17.6	5600	321	52	37	12	188	1.2	32.0	50	0.01
KL28-01	412	415.1	2.45	24500	3.52	16.5	1020	128	39	18	5	58	4.5	13.5	32	0.01
KL28-01	415.1	418.1	2.63	26300	3.61	17.2	2600	107	60	18	7	70	5.7	26.7	43	0.01
KL28-01	418.1	421.1	1.75	17500	2.92	11.5	1600	58	76	28	12	53	2.2	24.8	34	0.01
KL28-01	421.1	424.1	1.72	17200	3.53	12.7	2700	381	130	129	21	51	8	16.4	49	0.01
KL28-01	424.1	427.1	1.86	18600	3.41	20	1770	97	65	171	20	53	2	22.2	41	0.01
KL28-01	427.1	430.1	1.82	18200	3.01	19.2	20400	344	66	57	37	134	6.3	26.2	50	0.01
KL28-01	430.1	433.1	2.02	20200	2.7	30	7400	110	120	40	29	84	1.8	15.7	68	0.01
KL28-01	433.1	434.6	0.43	4300	0.44	10.4	15900	136	65	146	50	30	0.4	21.4	88	0.01
KL28-01	434.6	441.1	0.518	5180	0.56	4.8	1010	107	360	3700	20	6	1.1	15.9	122	0.29
KL28-01	441.1	445.1	0.05	500	0.11	0.1	170	68	18	430	7	4	0.7	2.8	83	0.01
KL28-01	445.1	448.5	0.042	420	0.09	0.1	108	50	24	153	10	4	0.5	4.0	56	0.01
KL28-01	448.5	451.4	0.042	420	0.07	0.1	113	46	21	183	22	4	0.4	4.3	78	0.01
KL28-01	451.4	454.1	0.041	410	0.12	0.6	154	47	26	123	28	2	0.4	3.3	34	0.01
KL28-01	454.1	456.8	0.24	2400	0.4	4.3	214	58	200	102	58	13	0.6	9.8	60	0.01
KL28-01	456.8	460.1	0.26	2600	0.42	2.8	2060	680	73	60	80	10	1	11.8	31	0.15
KL28-01	460.1	463.1	0.066	660	0.13	1.3	174	110	32	25	14	4	0.5	3.3	28	0.12
KL28-01	463.1	466.1	0.0131	131	0.09	0.1	177	75	5	7	2	1	0.4	2.0	26	0.01
KL28-01	466.1	468.6	0.094	940	0.13	1	279	83	23	5	2	2	0.5	3.0	30	0.01
KL28-01	468.6	469.9	0.5	5000	1.22	34.6	51100	58700	280	170	34	3	34	11.8	81	0.13
KL28-01	469.9	472.2	0.106	1060	0.52	4	5100	1940	35	145	55	8	1.7	10.5	33	0.01
KL28-01	472.2	474.6	0.0365	365	0.22	6.5	4580	3200	20	21	60	3	5.2	14.0	30	0.01
KL28-01	474.6	477.2	0.0142	142	0.1	2.4	4780	625	11	5	8	2	0.7	3.3	24	0.01
KL28-01	477.2	478.6	0.0154	154	0.15	0.9	1240	340	27	6	2	1	0.01	1.8	23	0.01
KL28-01	478.6	481	0.048	480	0.18	0.9	1850	610	110	10	8	1	0.7	4.8	22	0.21
KL28-01	481	484.1	0.065	650	0.09	0.8	830	193	52	7	5	1	0.2	2.1	25	0.01
KL28-01	484.1	488.1	0.071	710	0.19	1.9	1930	780	120	23	12	3	1.6	4.0	24	0.21
KL28-01	488.1	491.5	1.36	13600	0.7	9.9	2700	1120	67	34	16	14	2.5	9.0	48	0.01
KL28-01	491.5	493.1	0.117	1170	0.22	1.5	710	140	30	3	4	3	0.01	3.5	24	0.01
KL28-01	493.1	496.1	0.5	5000	0.51	9.4	8600	560	150	35	76	8	0.7	16.8	30	0.01
KL28-01	496.1	498.1	1.36	13600	0.74	26.9	5600	1500	270	35	138	7	0.8	7.9	42	0.01
KL28-01	498.1	500.7	2.32	23200	2.16	20.9	5800	700	78	28	34	54	1.5	35.0	51	0.01
KL28-01	500.7	502.8	0.98	9800	1.23	14.3	800	110	300	28	10	14	1.9	15.5	46	0.12
KL28-01	502.8	505.1	0.61	6100	0.65	5.7	3710	102	260	12	6	8	2.6	9.3	24	0.01
KL28-01	505.1	508.1	0.35	3500	0.25	2.4	600	104	310	3	2	15	3.5	6.3	29	0.01
KL28-01	508.1	511.1	0.478	4780	0.31	4.1	1120	760	210	12	2	23	1.7	8.3	30	0.11
KL28-01	511.1	514.1	0.72	7200	0.21	3.1	1600	540	460	48	3	15	4.5	6.3	50	0.18
KL28-01	514.1	517.1	1	10000	1.08	13.5	42100	4000	1260	9	9	46	19	5.8	52	2.19
KL28-01	517.1	520.1	0.95	9500	0.69	9.3	12700	1320	390	9	10	18	5	8.0	40	0.38
KL28-01	520.1	523.1	1.08	10800	0.64	20.1	1650	2300	570	40	44	26	3.2	14.0	95	0.01
KL28-01	523.1	526.1	0.476	4760	0.37	5	3590	450	370	9	10	19	2.6	7.8	30	0.19
KL28-01	526.1	529.1	0.86	8600	0.35	8.5	2400	610	290	13	12	14	1.4	8.0	38	0.01
KL28-01	529.1	532.1	1.03	10300	1.43	2.5	132	24	2	4	1	7	0.01	4.3	9	0.01
KL28-01	532.1	535.1	0.58	5800	0.5	6.2	10400	3000	560	4	14	8	1.7	11.8	28	0.31
KL28-01	535.1	537.6	0.98	9800	0.29	7	1060	219	79	5	4	28	2.5	9.5	33	0.01
KL28-01	537.6	539.6	0.25	2500	0.27	3.5	460	164	41	12	5	29	1.4	5.2	21	0.01
KL28-01	539.6	541.3	0.107	1070	0.15	2	970	165	34	3	7	5	0.01	5.3	18	0.01
KL28-01	541.3	544.1	1.25	12500	0.91	9.5	1280	118	36	64	18	70	1.5	17.0	67	0.01
KL28-01	544.1	547.1	0.73	7300	0.75	10.3	3300	117	52	12	30	26	0.7	25.8	29	0.01
KL28-01	547.1	549.4	1.05	10500	1.2	12.7	750	74	33	21	24	22	0.3	36.5	61	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL28-01	549.4	552.4	1.6	16000	1.42	12	780	197	170	18	14	95	2.8	21.6	84	0.01
KL28-01	552.4	555.5	2.05	20500	1.04	16.5	317	86	65	67	13	132	0.8	25.5	65	0.01
KL28-01	555.5	557.6	2.26	22600	1.68	19.3	369	40	51	1100	7	59	0.7	16.5	40	0.01
KL28-01	557.6	560.1	1.4	14000	1.3	9	407	115	81	23	18	57	3.8	14.5	78	0.01
KL28-01	560.1	561.9	0.65	6500	0.28	4.6	325	32	8	106	4	3	0.2	11.1	30	0.01
KL28-01	561.9	564.8	1.34	13400	1.28	12.3	1410	750	68	7	17	34	3.8	20.0	23	0.01
KL28-01	564.8	567.9	1.15	11500	0.96	12.6	7300	1700	46	15	22	22	2.5	21.8	38	0.01
KL28-01	567.9	571	1.35	13500	0.88	10.7	4300	41	27	20	38	25	0.4	20.8	36	0.01
KL28-01	571	574.1	1.26	12600	0.83	11.1	5800	186	28	11	108	13	0.3	40.3	42	0.01
KL28-01	574.1	577.1	1.34	13400	0.84	5	363	8	6	16	5	23	0.2	16.3	24	0.01
KL28-01	577.1	580.1	0.99	9900	0.5	2.6	157	13	6	4	4	21	0.01	11.0	20	0.01
KL28-01	580.1	583.1	1.18	11800	0.57	4.2	250	19	7	31	3	31	0.01	19.8	24	0.01
KL28-01	583.1	586.1	0.65	6500	0.37	2.8	255	57	17	9	4	26	0.2	19.2	38	0.01
KL28-01	586.1	589.1	1.42	14200	0.53	4.5	112	21	8	116	3	36	0.01	25.8	24	0.01
KL28-01	589.1	590.9	0.78	7800	0.36	2.7	107	9	6	84	2	18	0.01	17.0	27	0.01
KL28-01	590.9	593.9	1.47	14700	0.5	8.7	400	32	10	45	8	18	0.2	32.0	60	0.01
KL28-01	593.9	596.9	1.55	15500	0.7	10.1	680	23	12	54	7	47	0.3	25.8	56	0.01
KL28-01	596.9	601.1	2.25	22500	0.53	11.6	670	41	25	88	12	66	0.6	34.5	102	0.01
KL28-01	601.1	604.7	2.33	23300	0.36	11.7	403	76	31	196	58	60	2.2	38.0	192	0.01
KL28-01	604.7	607.1	1.7	17000	0.33	10.5	206	101	35	90	202	42	1.8	30.8	209	0.01
KL28-01	607.1	610.1	1.83	18300	0.48	13.6	2500	315	27	35	46	50	0.4	39.5	118	0.01
KL28-01	610.1	613.1	2.25	22500	0.8	9	680	30	13	47	5	44	0.3	21.9	67	0.01
KL28-01	613.1	615.1	2.05	20500	0.95	6.5	345	20	10	50	2	28	0.01	14.9	54	0.01
KL28-01	615.1	618.1	1.78	17800	0.42	4.8	154	8	6	99	3	26	0.01	22.2	80	0.01
KL28-01	618.1	621.1	1.04	10400	0.56	3.3	100	8	8	67	3	20	0.2	13.8	88	0.01
KL28-01	621.1	624	1.01	10100	0.59	2.6	50	9	10	46	2	36	0.01	27.0	83	0.01
KL28-01	624	627.3	0.519	5190	0.3	1.4	54	9	18	41	3	19	0.6	26.3	93	0.01
KL28-01	627.3	631.1	0.98	9800	0.76	3.7	59	7	17	20	6	19	0.8	21.5	100	0.01
KL28-01	631.1	634.1	0.79	7900	0.7	2.9	55	9	19	26	4	27	1.2	25.3	74	0.01
KL28-01	634.1	637.1	1.77	17700	1.06	4.1	64	8	18	14	3	17	1.2	17.3	51	0.01
KL28-01	637.1	640.1	1.23	12300	0.58	2.5	54	6	26	3	2	11	0.4	12.5	44	0.01
KL28-01	640.1	641.6	1.9	19000	1.11	5.3	89	7	14	10	2	44	0.01	19.2	51	0.01
KL28-01	641.6	644.1	0.94	9400	0.54	3.5	73	9	20	8	11	20	1.6	29.9	76	0.01
KL28-01	644.1	647.1	1.54	15400	1.05	8.8	120	7	15	23	7	29	0.01	26.2	73	0.01
KL28-01	647.1	649.1	1.3	13000	0.93	5.5	105	1	24	9	9	52	1.6	39.4	142	0.01
KL28-01	649.1	652.1	0.58	5800	0.66	2	75	6	56	7	9	24	4.1	19.0	94	0.01
KL28-01	652.1	655.1	0.96	9600	0.65	2.6	39	9	15	27	5	56	0.01	46.0	103	0.01
KL28-01	655.1	658.1	0.88	8800	0.35	1.8	46	13	17	83	2	53	0.2	19.5	60	0.12
KL28-01	658.1	661.1	0.86	8600	0.3	1.7	44	12	7	35	2	26	0.01	17.5	65	0.11
KL28-01	661.1	664.1	0.86	8600	0.64	2.6	43	8	18	13	2	17	0.6	15.5	60	0.01
KL28-01	664.1	667.1	1.07	10700	0.7	2.8	50	6	20	21	2	20	0.4	14.0	73	0.01
KL28-01	667.1	670.1	0.84	8400	0.67	2.4	48	7	27	34	2	41	0.7	15.8	65	0.13
KL28-01	670.1	673.1	1	10000	0.48	1.6	56	7	16	73	2	21	0.3	14.0	84	0.11
KL28-01	673.1	676.1	2.29	22900	0.84	4.8	47	8	6	90	0.01	45	0.01	26.8	82	0.01
KL28-01	676.1	679.1	1.07	10700	0.56	3	54	7	14	24	2	38	0.01	53.5	82	0.01
KL28-01	679.1	682.1	0.95	9500	0.75	2.9	56	8	22	13	2	20	1	23.2	73	0.01
KL28-01	682.1	685.1	0.65	6500	0.7	3.6	78	11	36	154	82	14	1.8	12.9	101	0.01
KL28-01	685.1	688.1	0.77	7700	0.8	3.6	86	12	22	14	46	14	8.9	16.0	78	0.01
KL28-01	688.1	691.1	0.57	5700	0.62	2.3	160	10	37	32	3	15	22	9.5	48	0.01
KL28-01	691.1	694.1	0.75	7500	0.45	3.2	273	27	41	41	50	18	6.5	22.3	93	0.01
KL28-01	694.1	697.1	0.53	5300	0.39	4.6	550	27	47	10	20	12	0.6	19.0	53	0.01
KL28-01	697.1	700.1	1.03	10300	0.51	4.7	391	48	54	11	5	17	0.5	18.5	43	0.01
KL28-01	700.1	703.1	0.55	5500	0.57	6.8	2620	43	51	4	32	8	0.6	13.0	40	0.01
KL28-01	703.1	706.1	0.54	5400	0.37	3.7	660	57	26	29	7	11	0.7	19.0	35	0.11
KL28-01	706.1	709.1	0.42	4200	0.4	1.9	154	14	29	11	2	26	9.1	22.0	60	0.01
KL28-01	709.1	712.1	0.95	9500	0.65	4.9	560	14	25	29	4	19	0.4	19.0	25	0.01
KL28-01	712.1	715.1	1.09	10900	1.11	4.3	392	13	18	7	3	40	7.1	19.3	58	0.01
KL28-01	715.1	718.1	0.91	9100	0.88	6.9	308	10	31	181	5	24	0.4	18.3	35	0.01
KL28-01	718.1	721.1	0.461	4610	0.46	3.1	240	14	62	6	10	35	12.4	47.0	45	0.01
KL28-01	721.1	724.1	1.06	10600	0.96	8.3	254	16	42	6	8	17	1.2	20.8	33	0.01
KL28-01	724.1	727.1	0.7	7000	1.09	4.2	214	20	37	31	5	15	1.5	19.5	43	0.1
KL28-01	727.1	730.1	0.68	6800	0.46	2.4	87	10	11	6	5	18	0.9	38.2	54	0.01
KL28-01	730.1	733.1	1	10000	0.76	3.1	214	16	20	25	4	19	1.9	11.8	40	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL28-01	733.1	736.1	0.56	5600	0.55	2.7	165	25	24	30	4	14	0.6	13.3	25	0.01
KL28-01	736.1	739.1	0.99	9900	0.61	1.9	129	20	10	105	1	26	0.7	11.8	28	0.01
KL28-01	739.1	742.1	0.65	6500	0.46	2	140	23	16	16	1	20	1	8.3	38	0.01
KL28-01	742.1	745.1	2.06	20600	1.33	4.4	136	12	10	114	2	36	0.7	14.5	49	0.11
KL28-01	745.1	748.1	0.77	7700	0.5	1.8	48	16	13	46	1	28	0.5	10.8	28	0.11
KL28-01	748.1	751.1	0.48	4800	0.53	4.6	710	390	15	14	3	15	1.9	16.8	50	0.01
KL28-01	751.1	753	0.56	5600	0.5	2	136	16	34	25	3	19	1.5	12.5	35	0.1
KL28-01	753	754.5	0.18	1800	0.23	0.6	65	16	9	8	4	6	0.3	0.5	28	0.01
KL28-01	754.5	757.1	1.39	13900	1.37	4.8	188	14	30	16	4	24	1	13.5	30	0.01
KL28-01	757.1	760.1	1.4	14000	1.88	5.1	205	17	32	70	6	20	1.4	14.0	43	0.01
KL28-01	760.1	763.1	0.4	4000	0.4	2.3	357	500	24	24	3	12	2.1	18.3	48	0.01
KL28-01	763.1	766.1	1.39	13900	0.68	5.4	113	17	19	48	4	34	0.3	18.3	28	0.01
KL28-01	766.1	769.1	1.1	11000	0.44	6	110	20	43	195	12	22	0.3	21.0	80	0.01
KL28-01	769.1	772.1	1.09	10900	0.62	5.6	145	91	160	198	54	19	0.4	20.8	35	0.01
KL28-01	772.1	775.1	1	10000	0.45	3.3	92	17	13	450	1	14	0.01	9.8	30	0.01
KL28-01	775.1	777.1	1.37	13700	0.63	2.9	91	10	6	108	7	15	0.01	12.3	30	0.01
KL28-01	777.1	780.1	0.54	5400	0.21	1.2	56	10	8	30	5	14	0.01	8.8	25	0.01
KL28-01	780.1	781.6	0.57	5700	0.26	1.7	136	10	9	38	4	9	0.01	8.5	25	0.01
KL28-01	781.6	785.4	0.34	3400	0.13	1.7	115	32	12	15	3	9	0.2	4.5	27	0.01
KL28-01	785.4	788.4	1.01	10100	0.8	4.5	420	60	20	20	7	22	0.2	15.3	63	0.01
KL28-01	788.4	791.4	1.3	13000	1.6	5.6	310	18	27	12	6	25	0.3	41.8	40	0.01
KL28-01	791.4	793.1	1.3	13000	1.56	7.7	248	24	26	88	38	21	0.7	14.0	38	0.01
KL28-01	793.1	796.1	0.83	8300	0.82	9.1	1190	62	33	22	123	22	0.3	12.0	25	0.01
KL28-01	796.1	798	0.84	8400	0.76	8.7	990	171	34	8	20	19	0.7	5.5	35	0.01
KL28-01	798	800.3	0.49	4900	0.65	4.7	1030	216	29	4	8	14	0.5	6.5	35	0.01
KL28-01	800.3	802.1	0.169	1690	0.35	2.8	1650	320	20	3	11	9	0.01	2.3	25	0.01
KL28-01	802.1	805.1	0.083	830	0.17	0.9	1010	308	17	3	13	5	0.01	1.6	29	0.01
KL28-01	805.1	808.1	0.34	3400	0.51	2.6	910	147	24	3	5	12	0.2	3.8	30	0.01
KL28-01	808.1	811.1	0.346	3460	0.45	1.8	306	61	41	2	3	15	0.01	5.5	25	0.01
KL28-01	811.1	814.1	0.062	620	0.08	0.1	62	30	6	3	1	3	0.01	1.8	20	0.01
KL28-01	814.1	817.1	1.02	10200	1.41	2.4	139	24	3	2	1	10	0.01	4.5	13	0.01
KL28-01	817.1	820.1	0.115	1150	0.04	0.1	75	40	10	2	2	4	0.01	2.5	15	0.01
KL28-01	820.1	823.1	0.13	1300	0.07	0.1	54	23	9	4	2	4	0.01	2.3	15	0.01
KL28-01	823.1	824.9	0.034	340	0.06	0.1	17	12	2	2	1	3	0.01	1.8	18	0.01
KL28-02	0	2.5	0.0024	24	0.02	0.8	152	580	5	1	0.01	1	1.5	1.3	17	0.01
KL28-02	2.5	5.5	0.003	30	0.04	0.7	570	269	6	4	0.01	1	1.5	1.3	14	0.01
KL28-02	5.5	8.5	0.0015	15	0.03	0.1	121	91	6	3	0.01	1	0.8	1.6	22	0.01
KL28-02	8.5	11.5	0.0036	36	0.02	0.1	111	59	9	1	0.01	1	0.7	0.9	23	0.01
KL28-02	11.5	14.5	0.0005	5	0.01	0.1	26	27	13	1	0.01	1	0.3	1.1	27	0.01
KL28-02	14.5	17.5	0.0005	5	0.03	0.1	83	54	7	1	0.01	1	0.2	3.4	23	0.01
KL28-02	17.5	20.5	0.0005	5	0.01	0.1	42	34	5	1	0.01	1	0.2	1.4	17	0.01
KL28-02	20.5	23.5	0.0008	8	0.01	0.1	49	26	7	1	0.01	1	0.4	1.6	24	0.01
KL28-02	23.5	26.5	0.0013	13	0.01	0.1	42	28	6	1	0.01	1	0.4	1.4	31	0.01
KL28-02	26.5	29.5	0.0011	11	0.01	0.1	76	30	6	1	0.01	1	0.01	1.4	29	0.01
KL28-02	29.5	32.5	0.001	10	0.01	0.1	30	23	3	4	0.01	1	0.01	1.0	30	0.01
KL28-02	32.5	34.8	0.0011	11	0.01	0.1	44	32	5	1	0.01	1	0.2	1.7	26	0.01
KL28-02	34.8	36.9	0.0008	8	0.01	0.1	74	79	14	1	0.01	1	0.5	1.6	23	0.01
KL28-02	36.9	38.5	0.0028	28	0.01	1.6	98	520	14	1	3	1	1.5	7.7	29	0.01
KL28-02	38.5	41.5	0.0184	184	0.02	2	113	82	23	3	2	1	2.5	5.7	77	0.01
KL28-02	41.5	43.8	0.0178	178	0.06	1.2	85	151	30	5	2	1	2	3.9	70	0.01
KL28-02	43.8	45.7	0.047	470	0.13	2.6	640	234	47	7	3	1	1.8	6.5	123	0.01
KL28-02	45.7	47.5	0.084	840	0.46	31.2	12700	15300	240	6	28	1	24	88.0	27	0.1
KL28-02	47.5	50.5	0.0148	148	0.14	7.9	620	2270	48	4	12	1	4.4	6.3	31	0.01
KL28-02	50.5	53.5	0.0124	124	0.18	2.1	157	1070	41	1	1	1	5.9	1.2	30	0.01
KL28-02	53.5	56.5	0.0118	118	0.06	9.4	272	4680	26	11	7	1	3.6	2.6	37	0.01
KL28-02	56.5	59.5	0.0326	326	0.25	7.9	440	4680	39	6	5	1	3.7	5.2	36	0.01
KL28-02	59.5	62.5	0.0085	85	0.05	1.7	126	1500	21	5	1	1	2.8	0.0	18	0.01
KL28-02	62.5	65	0.0104	104	0.02	1.2	105	480	13	7	1	1	1.1	1.0	19	0.01
KL28-02	65	68	0.0075	75	0.02	0.7	72	209	16	13	0.01	1	2	0.7	19	0.01
KL28-02	68	71	0.0058	58	0.01	0.1	40	85	11	5	0.01	1	1.2	0.0	16	0.01
KL28-02	71	72.6	0.0114	114	0.01	0.1	41	135	8	5	0.01	1	0.4	0.7	20	0.01
KL28-02	72.6	75.6	0.0057	57	0.01	0.1	25	66	2	4	0.01	1	0.01	0.9	13	0.01
KL28-02	75.6	78.7	0.0065	65	0.01	0.1	27	53	4	7	0.01	1	0.01	0.7	14	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL28-02	78.7	81.5	0.0035		35	0.01	0.1	31	60	4	6	0.01	1	0.3	0.8	7	0.01
KL28-02	81.5	82.9	0.0071		71	0.01	0.1	27	42	9	7	0.01	1	1.3	0.0	17	0.01
KL28-02	82.9	84.7	0.0027		27	0.01	0.1	19	34	3	4	0.01	1	0.01	0.0	9	0.01
KL28-02	84.7	87.7	0.0033		33	0.02	1.5	106	335	11	3	0.01	1	2	0.0	12	0.01
KL28-02	87.7	90.7	0.0063		63	0.02	0.1	31	60	11	3	0.01	1	0.4	0.9	16	0.01
KL28-02	90.7	93.7	0.0091		91	0.03	7.6	980	1510	20	1	0.01	1	4	3.7	21	0.01
KL28-02	93.7	96.5	0.0071		71	0.08	6.5	950	1600	16	4	0.01	1	5.9	3.7	25	0.01
KL28-02	96.5	99.1	0.0056		56	0.08	3.7	560	1480	13	4	0.01	1	5.1	1.9	25	0.01
KL28-02	99.1	102.2	0.0051		51	0.07	3	230	500	13	4	0.01	1	2.2	1.6	18	0.01
KL28-02	102.2	105.5	0.0056		56	0.09	3.6	262	480	13	6	0.01	1	2.6	1.7	18	0.01
KL28-02	105.5	108	0.0045		45	0.05	2.8	229	390	8	4	0.01	1	3.1	1.5	20	0.01
KL28-02	108	110.5	0.0028		28	0.04	4.6	530	760	5	1	0.01	1	3.8	2.7	19	0.01
KL28-02	110.5	113.5	0.0075		75	0.03	8.2	1320	1330	18	1	0.01	1	4.7	4.5	23	0.01
KL28-02	113.5	116.2	0.64		6400	0.15	7.1	395	269	170	28	0.01	6	40	4.3	174	0.01
KL28-02	116.2	119	0.0041		41	0.04	3.4	333	740	6	3	0.01	1	3.1	1.9	23	0.01
KL28-02	119	121.5	0.0031		31	0.02	2.5	208	470	3	1	0.01	1	2.1	2.2	23	0.01
KL28-02	121.5	124.5	0.0027		27	0.02	1.2	212	275	1	1	0.01	1	1.2	0.8	25	0.01
KL28-02	124.5	127	0.0042		42	0.03	3.8	1060	540	7	1	0.01	1	2.1	3.0	23	0.01
KL28-02	127	130	0.0022		22	0.02	1.7	121	277	4	3	0.01	1	1.3	1.7	26	0.01
KL28-02	130	133	0.0019		19	0.03	4.1	182	1080	6	4	0.01	1	3.8	2.1	25	0.01
KL28-02	133	136	0.0025		25	0.03	5.1	289	1980	6	5	0.01	1	4.6	2.0	22	0.01
KL28-02	136	139	0.0021		21	0.02	1	143	201	4	5	0.01	1	0.9	1.1	21	0.01
KL28-02	139	142	0.0022		22	0.02	1.5	223	310	6	6	0.01	1	0.8	1.0	17	0.01
KL28-02	142	144.8	0.0019		19	0.02	1.5	450	361	3	6	0.01	1	1.1	1.2	15	0.01
KL28-02	144.8	147.8	0.0022		22	0.02	2.3	670	480	6	7	0.01	1	1.6	1.6	12	0.01
KL28-02	147.8	150.2	0.0031		31	0.03	1.8	410	590	4	7	0.01	1	1.4	1.0	17	0.01
KL28-02	150.2	152.2	0.0068		68	0.04	5.2	2040	2050	14	8	0.01	1	3.2	2.6	10	0.01
KL28-02	152.2	155.2	0.0034		34	0.02	1.6	700	660	7	6	0.01	1	2	1.6	15	0.01
KL28-02	155.2	158.5	0.0129		129	0.06	1.3	430	600	16	9	0.01	1	1.1	1.7	13	0.01
KL28-02	158.5	161.5	0.0046		46	0.03	1.1	157	260	11	5	0.01	1	0.7	1.2	11	0.01
KL28-02	161.5	164.5	0.0057		57	0.02	1	382	312	7	8	0.01	1	0.8	1.2	10	0.01
KL28-02	164.5	167.2	0.0059		59	0.02	6.1	1810	1860	9	12	2	1	2.7	3.9	11	0.01
KL28-02	167.2	170	0.0059		59	0.18	11.9	204	670	200	15	3	13	5.3	7.0	47	0.01
KL28-02	170	172.5	0.0035		35	0.02	1.9	162	230	10	10	1	1	0.8	1.2	12	0.01
KL28-02	172.5	175.8	0.0047		47	0.09	4.5	1070	1440	9	14	1	1	3.5	3.8	19	0.01
KL28-02	175.8	178	0.0033		33	0.03	2.3	520	750	4	29	1	1	1.4	2.6	15	0.01
KL28-02	178	180.8	0.085		850	0.07	7.6	2460	3630	14	8	2	1	6	11.8	18	0.01
KL28-02	180.8	183.7	0.0042		42	0.04	2.4	740	810	5	8	1	1	1.7	3.1	15	0.01
KL28-02	183.7	186.7	0.0042		42	0.04	1.8	317	470	8	6	1	1	1.1	2.1	15	0.01
KL28-02	186.7	189	0.0164		164	0.05	2	470	328	8	32	3	1	0.9	4.5	17	0.01
KL28-02	189	192	0.0298		298	0.2	6.7	2350	1810	38	30	9	1	4.4	6.8	19	0.1
KL28-02	192	194.9	0.0112		112	0.14	4.2	1040	1340	13	22	6	1	1.9	4.8	19	0.01
KL28-02	194.9	198	0.054		540	0.14	10.4	7200	6700	140	13	6	1	7.7	7.0	24	0.16
KL28-02	198	201	0.112		1120	0.25	13.2	5100	3400	140	16	27	1	11.1	15.5	48	0.17
KL28-02	201	204	0.069		690	0.52	19.3	9200	15500	130	33	32	1	9.8	23.0	47	0.26
KL28-02	204	207	0.093		930	0.34	16.9	7100	1780	86	31	44	1	1.7	12.3	32	0.01
KL28-02	207	210	0.095		950	0.33	19.2	3970	2820	67	29	50	1	1.8	20.8	38	0.01
KL28-02	210	213	0.97		9700	2.03	62	40200	6000	230	7	380	14	2.3	168.0	115	0.29
KL28-02	213	216	1.56		15600	1.68	47	403	630	130	17	323	28	0.9	50.5	138	0.01
KL28-02	216	219	0.96		9600	2.01	33	3600	700	93	64	233	12	1.2	69.0	122	0.01
KL28-02	219	221	1.33		13300	1.4	13.8	207	90	160	590	187	16	3.9	45.5	150	0.13
KL28-02	221	224.5	0.188		1880	0.27	2.2	59	38	130	700	7	6	0.6	19.5	301	0.01
KL28-02	224.5	227.5	0.35		3500	0.72	3.9	223	127	1001	1200	12	10	2.5	22.3	236	0.1
KL28-02	227.5	230.2	0.347		3470	0.64	3.5	600	183	46	1180	10	9	2.2	24.3	306	0.1
KL28-02	230.2	233	1.51		15100	1.38	9.3	570	210	170	73	4	25	5.4	31.0	193	0.22
KL28-02	233	236	1.08		10800	1.24	6.6	360	114	120	600	4	25	2.7	45.5	151	0.15
KL28-02	236	239	0.6		6000	0.7	4.4	283	77	95	704	3	17	1	24.0	214	0.18
KL28-02	239	242	0.5		5000	0.6	2.5	287	43	40	69	1	18	1.8	12.0	140	0.11
KL28-02	242	245	0.68		6800	0.76	3	309	76	95	83	3	37	2.4	38.3	221	0.22
KL28-02	245	248	1.95		19500	1.39	7	164	29	69	895	2	126	1	39.3	146	0.4
KL28-02	248	251	0.69		6900	0.68	2	116	26	21	48	2	25	1.3	19.8	197	0.11
KL28-02	251	254	0.65		6500	1.2	3	242	44	66	113	2	20	2.2	18.8	168	0.21
KL28-02	254	257	0.75		7500	1.42	4.8	190	33	30	62	2	21	1.4	19.3	242	0.2

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL28-02	257	260	0.73	7300	1.84	3.8	133	16	25	57	1	21	1.1	26.0	135	0.31
KL28-02	260	263	1.09	10900	1.63	4	94	9	12	46	1	35	0.5	39.5	72	0.1
KL28-02	263	266	1.5	15000	1.86	4.8	106	8	11	48	1	30	0.7	38.5	55	0.01
KL28-02	266	269	3.65	36500	3.44	13.1	301	109	350	35	1	101	1	36.5	129	1.15
KL28-02	269	272	8.42	84200	6.86	16.8	6300	2600	740	924	0.01	141	0.8	57.5	139	2
KL28-02	272	274.8	3.23	32300	3.9	8	194	17	1	196	0.01	75	0.01	32.0	29	0.01
KL28-02	274.8	278	3.37	33700	3.66	9.2	155	9	0.01	86	0.01	131	0.01	40.0	48	0.01
KL28-02	278	281	2.18	21800	2.41	6.8	130	8	4	211	1	189	0.01	63.5	65	0.01
KL28-02	281	283.9	4.05	40500	4.56	12.5	153	12	1	191	1	265	0.01	39.5	71	0.01
KL28-02	283.9	286.8	3.4	34000	3.14	8.4	119	50	280	136	1	146	0.5	34.0	183	0.18
KL28-02	286.8	289.7	4.03	40300	3.94	13	120	28	220	72	0.01	201	0.3	41.0	144	0.28
KL28-02	289.7	292.8	4.2	42000	6.64	13.3	180	11	8	58	1	102	0.01	29.0	167	0.01
KL28-02	292.8	295.8	4.17	41700	5.97	11.6	268	11	5	165	1	92	0.3	38.5	202	0.01
KL28-02	295.8	298.8	3.33	33300	4.32	8	231	86	23	81	1	78	2.3	21.0	95	0.01
KL28-02	298.8	301.5	2.45	24500	3.57	6.8	86	21	13	149	1	111	0.3	26.5	217	0.01
KL28-02	301.5	304.5	7.73	77300	8.82	26.6	540	12	7	75	1	108	1.2	42.5	118	0.01
KL28-02	304.5	307.5	1.52	15200	1.62	5.1	35	8	5	423	1	52	0.3	37.3	188	0.01
KL28-02	307.5	310.5	2.21	22100	1.57	5.5	54	12	7	500	1	69	0.3	31.0	241	0.26
KL28-02	310.5	313.5	1.66	16600	2.57	9.5	200	24	66	600	1	147	1.8	73.2	237	0.01
KL28-02	313.5	316.5	6.46	64600	6.38	17.7	291	48	17	290	0.01	64	0.5	45.0	240	0.01
KL28-02	316.5	319.6	3.88	38800	5.37	13	236	12	0.01	42	1	47	0.2	20.0	128	0.01
KL28-02	319.6	322.6	3.14	31400	4.27	10.3	247	11	2	13	1	58	0.01	16.0	83	0.01
KL28-02	322.6	325.3	3.53	35300	4.74	14.4	440	12	12	17	2	55	0.7	32.0	279	0.01
KL28-02	325.3	328	2.16	21600	3.34	8.8	336	28	39	64	3	77	1	35.0	274	0.01
KL28-02	328	331	3.85	38500	4.22	15.6	570	136	410	225	1	80	7.3	47.0	248	0.2
KL28-02	331	334	1	10000	1	3.2	412	130	90	480	1	69	2.8	47.5	285	0.01
KL28-02	334	337	1.75	17500	1.68	5	77	31	96	320	1	75	1.3	42.0	423	0.01
KL28-02	337	340	1.62	16200	1.54	4.7	51	16	27	340	1	73	0.6	42.5	255	0.01
KL28-02	340	343	1.4	14000	1.86	5.7	55	16	24	275	2	68	0.6	41.5	336	0.15
KL28-02	343	346	2.07	20700	2.82	11.1	141	23	19	83	4	52	0.3	47.2	350	0.15
KL28-02	346	349	3.91	39100	4.32	23.8	590	35	45	3	3	25	1	42.0	217	0.01
KL28-02	349	352	1.81	18100	2.94	8.5	135	27	39	11	6	26	0.5	30.0	337	0.01
KL28-02	352	355	2.35	23500	3.06	16.1	357	21	44	14	7	80	0.7	38.0	289	0.01
KL28-02	355	358	2.38	23800	1.86	13.8	1320	24	61	7	10	71	0.5	32.0	322	0.01
KL28-02	358	361	1.8	18000	1.2	5.5	86	16	96	203	5	22	0.6	20.0	290	0.01
KL28-02	361	364	2.67	26700	2.62	18.7	363	23	82	730	7	13	0.5	33.0	265	0.01
KL28-02	364	367	3.22	32200	35.1	30	570	29	150	240	4	11	0.7	22.0	170	0.01
KL28-02	367	370	3.21	32100	17.3	43.7	1070	31	61	170	12	137	0.5	46.0	190	0.01
KL28-02	370	373	0.99	9900	3.56	8.4	254	37	140	163	46	15	1	48.8	293	0.01
KL28-02	373	376	3.48	34800	4.82	14	365	52	220	20	126	6	1.8	32.0	253	0.01
KL28-02	376	379	2.93	29300	3.02	33.5	620	101	270	11	224	3	1.8	31.0	256	0.01
KL28-02	379	382	0.52	5200	2.36	21.5	72000	750	200	3	334	10	2	83.2	195	0.01
KL28-02	382	385	1.51	15100	3.26	14.5	23200	154	170	10	250	1	3.4	18.0	151	0.01
KL28-02	385	385.6	0.47	4700	1.47	12	9300	1530	140	38	190	5	3	27.1	317	0.01
KL28-02	385.6	388	0.0314	314	0.42	1.7	1160	540	32	34	18	1	1.3	5.0	38	0.01
KL28-02	388	391	0.0112	112	0.2	2.3	2800	3800	40	3	2	3	1.9	6.7	29	0.01
KL28-02	391	394	0.075	750	0.27	0.9	1650	58	30	7	19	1	2.1	14.7	33	0.01
KL28-02	394	397	0.0335	335	0.16	0.7	395	272	50	15	3	3	1.2	5.5	37	0.01
KL28-02	397	400	0.0039	39	0.18	0.1	142	80	65	3	1	1	0.8	1.2	34	0.01
KL28-02	400	403	0.0168	168	0.49	1.3	1550	910	38	14	28	1	2.1	5.7	48	0.01
KL28-02	403	406	0.0195	195	0.17	1.3	325	170	43	21	22	3	2.8	4.0	35	0.01
KL28-02	406	409	0.0135	135	0.33	0.1	254	80	45	11	1	1	2	0.7	33	0.01
KL28-02	409	412	0.0112	112	0.25	0.8	520	393	38	8	3	1	1.9	6.2	43	0.01
KL28-02	412	415	0.0075	75	0.1	0.9	245	440	38	76	3	1	2.9	5.7	31	0.01
KL28-02	415	418	0.0075	75	0.47	2.5	580	2600	110	12	4	1	4	17.0	42	0.01
KL28-02	418	421	0.0036	36	0.57	0.1	117	52	160	19	0.01	3	2	1.7	48	0.01
KL28-02	421	424	0.0055	55	0.15	0.1	66	27	120	13	0.01	3	1.1	0.5	29	0.01
KL28-02	424	427	0.0231	231	0.22	2.6	720	660	110	21	2	1	5.1	3.8	48	0.01
KL28-02	427	430	0.0081	81	0.19	0.1	394	271	120	32	0.01	1	2.5	1.9	44	0.01
KL28-02	430	433	0.0072	72	0.23	0.1	199	110	160	54	1	1	2.8	1.5	43	0.01
KL28-02	433	436	0.0144	144	0.23	0.5	330	105	160	130	2	1	3	2.6	54	0.01
KL28-02	436	439	0.0115	115	0.09	2.9	2400	1500	74	19	5	1	2.6	7.5	32	0.01
KL28-02	439	442	0.0072	72	0.08	0.1	328	142	39	11	1	1	1.7	1.7	31	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL28-02	442	445	0.0115		115	0.05	8.2	7100	4400	27	3	12	1	4.9	19.8	35	0.01
KL28-02	445	448	0.0036		36	0.04	0.1	27	23	20	3	0.01	2	0.6	0.0	23	0.01
KL28-02	448	451	0.0038		38	0.06	0.1	208	155	19	2	0.01	1	1	1.2	25	0.01
KL28-02	451	454	0.0049		49	0.08	0.1	293	205	20	4	0.01	1	1	1.2	23	0.01
KL28-02	454	457	0.0104		104	0.04	0.1	61	34	18	5	0.01	1	0.4	1.0	23	0.01
KL28-02	457	460	0.0102		102	0.19	0.1	130	65	40	27	0.01	1	2	1.7	33	0.01
KL28-02	460	462.5	0.0152		152	0.23	1.1	630	225	56	26	2	3	2.4	1.5	56	0.01
KL28-02	462.5	465	0.0174		174	0.3	1.1	125	110	110	340	6	4	4.5	2.0	55	0.01
KL28-02	465	468	0.0078		78	0.11	0.1	72	32	38	19	0.01	1	0.8	0.0	26	0.01
KL28-02	468	471	0.0132		132	0.17	0.7	229	211	48	8	0.01	1	2.6	1.9	46	0.01
KL28-02	471	474	0.0067		67	0.19	0.1	30	33	48	19	0.01	1	1.6	1.0	40	0.01
KL28-02	474	477	0.0058		58	0.15	0.5	150	147	29	4	2	1	1	14.0	23	0.01
KL28-02	477	480	0.0061		61	0.3	0.6	76	31	110	24	1	3	2.2	3.0	42	0.01
KL28-02	480	483	0.0053		53	0.58	1.5	62	34	120	14	0.01	1	3.3	8.2	48	0.01
KL28-02	483	485.5	0.0054		54	0.2	0.1	76	30	78	11	0.01	3	1.3	2.5	39	0.01
KL28-02	485.5	488.5	0.0058		58	0.12	0.1	63	20	30	7	0.01	1	1.5	0.8	25	0.01
KL28-02	488.5	491.5	0.0048		48	0.11	0.1	90	28	29	2	0.01	1	1.8	1.1	24	0.01
KL28-02	491.5	494.5	0.0043		43	0.11	0.5	75	33	44	7	0.01	4	1.7	0.6	23	0.01
KL28-02	494.5	497.5	0.0048		48	0.08	3.1	2200	1800	40	5	0.01	2	5.1	7.7	26	0.01
KL28-02	497.5	500.5	0.003		30	0.16	1	560	410	42	3	0.01	3	2.3	2.5	22	0.01
KL28-02	500.5	503.5	0.0041		41	0.1	1.7	1440	860	42	3	0.01	1	5.2	3.0	25	0.01
KL28-02	503.5	506.5	0.0095		95	0.33	8.3	3050	1500	160	2	0.01	3	24	10.6	34	0.01
KL28-02	506.5	509.5	0.0058		58	3.3	2.7	172	80	550	3	0.01	4	55	7.5	53	0.01
KL28-02	509.5	512.5	0.0039		39	0.23	2.3	262	960	71	1	0.01	1	7.4	5.2	26	0.01
KL28-02	512.5	515.5	0.0018		18	0.23	0.1	50	29	49	9	0.01	3	4.5	0.7	25	0.01
KL28-02	515.5	518.5	0.0022		22	0.19	0.1	103	43	100	3	0.01	3	5.8	2.2	30	0.01
KL28-02	518.5	521.5	0.0016		16	0.23	0.1	120	31	84	4	0.01	4	8.9	1.2	27	0.01
KL28-02	521.5	524.5	0.0039		39	1.03	0.1	214	168	105	4	0.01	1	22	2.7	23	0.01
KL28-02	524.5	527.5	0.193		1930	0.75	2.5	367	132	250	11	7	3	24	7.2	36	0.01
KL28-02	527.5	530.5	0.0339		339	1.15	4.4	970	243	159	280	45	6	15.5	7.7	56	0.01
KL28-02	530.5	533.5	0.0089		89	0.21	1.8	233	156	98	560	18	12	2.7	5.0	110	0.01
KL28-02	533.5	536.5	0.026		260	0.31	10.8	6100	2400	46	35	40	28	3	0.0	178	0.01
KL28-02	536.5	539.5	0.33		3300	0.57	172	51400	30100	120	116	368	14	6.5	75.0	239	0.01
KL28-02	539.5	542.5	0.109		1090	0.52	64	17000	11600	77	42	137	9	2.9	47.0	345	0.01
KL28-02	542.5	545.5	0.058		580	0.25	14.8	5600	5200	44	15	35	5	6.4	7.3	430	0.01
KL28-02	545.5	548.5	0.0199		199	0.24	4.9	1530	1100	40	16	10	5	2.7	4.0	390	0.01
KL28-02	548.5	551.5	0.0178		178	0.28	7.1	1620	1090	33	9	25	8	1.7	6.5	321	0.01
KL28-02	551.5	554.5	0.0112		112	0.22	2.3	490	317	34	4	6	10	1.2	3.7	311	0.01
KL28-02	554.5	557.5	0.0201		201	0.12	2.9	850	410	29	43	5	1	1.2	2.5	300	0.01
KL28-02	557.5	560.5	0.0121		121	0.13	1.6	258	720	28	19	4	3	0.8	3.0	470	0.01
KL28-02	560.5	563.5	0.0169		169	0.24	1.1	72	90	48	13	3	8	3.6	3.5	375	0.01
KL28-02	563.5	566.5	0.0155		155	0.53	1.9	340	228	110	30	6	9	2.1	5.5	265	0.01
KL28-02	566.5	569.5	0.0125		125	0.27	5.9	1020	1260	43	114	15	3	0.9	4.0	230	0.01
KL28-02	569.5	572.5	0.078		780	0.37	17.6	12800	6700	130	235	41	1	3.2	26.5	72	0.01
KL28-02	572.5	575.5	0.0069		69	0.21	3.2	1620	1270	20	8	2	1	1.9	9.5	40	0.01
KL28-02	575.5	578.5	0.53		5300	0.72	27.1	2500	1900	220	1240	55	10	33	18.7	33	0.01
KL28-02	578.5	581.5	0.0391		391	0.27	13.6	9800	7300	46	37	7	1	9.8	30.3	33	0.01
KL28-02	581.5	584.5	0.0058		58	0.09	2.3	850	800	9	8	2	1	1.2	5.3	24	0.01
KL28-02	584.5	587.5	0.0395		395	0.29	17.5	14600	11800	27	18	4	1	14.4	31.6	33	0.01
KL28-02	587.5	590.5	0.0038		38	0.12	1.4	730	540	10	6	1	1	0.8	0.7	20	0.01
KL28-02	590.5	593.5	0.0017		17	0.05	0.6	262	340	3	1	0.01	1	0.9	0.0	20	0.01
KL28-02	593.5	596.5	0.0037		37	0.05	0.1	74	92	4	2	0.01	1	0.6	0.6	31	0.01
KL28-02	596.5	599.5	0.0014		14	0.03	0.1	63	156	4	5	0.01	1	0.5	0.6	26	0.01
KL28-02	599.5	602.5	0.0009		9	0.03	0.1	44	75	6	5	0.01	1	0.2	0.5	28	0.01
KL28-02	602.5	605.5	0.0043		43	0.09	4	213	3000	17	10	0.01	1	5.4	2.0	25	0.01
KL28-02	605.5	608.5	0.0418		418	0.45	6.6	11400	2200	51	29	0.01	1	6.9	7.0	37	0.01
KL28-02	608.5	611.5	0.0081		81	0.21	4.6	1850	2800	15	13	0.01	1	3.2	7.7	36	0.01
KL28-02	611.5	614.5	0.0035		35	0.06	0.1	120	94	4	6	0.01	1	0.5	1.7	29	0.01
KL28-02	614.5	617.5	0.0026		26	0.1	1.1	580	260	4	5	0.01	1	1	1.2	23	0.01
KL28-02	617.5	620.5	0.0097		97	0.23	1.2	227	175	33	7	0.01	1	2.2	4.0	32	0.01
KL28-02	620.5	623.5	0.0045		45	0.19	7.3	2300	7000	26	12	0.01	1	8.6	15.2	50	0.01
KL28-02	623.5	626.5	0.0017		17	0.15	1	110	119	12	8	0.01	3	0.7	3.0	33	0.01
KL28-02	626.5	629.5	0.0035		35	0.12	1.4	440	600	12	6	0.01	1	2	4.6	32	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL28-02	629.5	632.5	0.073		730	0.73	2.9	2100	132	68	48	122	6	4.5	15.3	84	0.01
KL28-02	632.5	635.5	0.0036		36	0.18	1.5	1640	950	24	12	2	4	3.9	8.5	32	0.01
KL28-02	635.5	638.5	0.0019		19	0.19	0.5	182	127	18	11	0.01	1	1.7	6.0	34	0.01
KL28-02	638.5	641.5	0.0259		259	0.35	1.7	1020	490	31	22	7	3	6.1	9.7	47	0.01
KL28-02	641.5	644.5	0.0031		31	0.25	0.7	530	284	14	7	0.01	4	1.1	2.7	21	0.01
KL28-02	644.5	647.5	0.072		720	0.08	2.5	367	180	55	9	0.01	4	2.1	4.7	22	0.01
KL28-02	647.5	650.5	0.0022		22	0.09	0.6	175	232	7	3	0.01	1	0.7	1.3	19	0.01
KL28-02	650.5	653	0.0014		14	0.06	0.1	48	27	3	3	0.01	1	0.4	0.0	15	0.01
KL28-02	653	656.2	0.0032		32	0.15	0.6	140	73	4	3	0.01	1	0.7	0.0	12	0.01
KL28-02	656.2	658.4	0.0052		52	0.06	0.1	50	47	8	4	0.01	1	1.3	1.2	16	0.01
KL28-03	0	3	0.0056		56	0.01	0.1	53	26	6	4	0.01	1	0.7	0.8	22	0.01
KL28-03	3	6	0.0025		25	0.01	0.1	395	122	8	2	0.01	1	1	0.6	15	0.01
KL28-03	6	9	0.0102		102	0.1	1.1	430	184	21	3	0.01	1	2.3	4.3	29	0.01
KL28-03	9	12	0.0092		92	0.01	0.1	47	42	6	2	0.01	1	0.6	0.9	24	0.01
KL28-03	12	15	0.0026		26	0.01	0.1	27	25	3	2	0.01	1	0.5	1.2	28	0.01
KL28-03	15	18	0.0028		28	0.01	0.1	44	43	6	2	0.01	1	0.6	0.7	31	0.01
KL28-03	18	21	0.0041		41	0.01	0.1	25	23	2	2	0.01	1	0.4	1.0	25	0.01
KL28-03	21	24	0.0029		29	0.01	0.1	104	361	4	1	0.01	1	1	2.2	24	0.01
KL28-03	24	27	0.006		60	0.02	0.1	195	87	7	1	0.01	1	1	1.2	25	0.01
KL28-03	27	30	0.0051		51	0.01	0.1	37	21	6	2	0.01	1	0.7	1.2	30	0.01
KL28-03	30	33	0.0036		36	0.01	0.1	27	16	2	1	0.01	1	0.4	1.5	30	0.01
KL28-03	33	36	0.003		30	0.01	0.1	73	22	4	1	0.01	1	0.3	1.0	36	0.01
KL28-03	36	39	0.0037		37	0.01	0.1	40	23	2	1	0.01	1	0.3	0.9	29	0.01
KL28-03	39	42	0.0032		32	0.01	0.1	37	32	4	1	0.01	1	0.4	1.3	23	0.01
KL28-03	42	45	0.0046		46	0.01	1.1	191	540	4	1	0.01	1	1.9	2.6	32	0.01
KL28-03	45	48	0.0133		133	0.01	0.7	68	194	8	1	1	1	3.8	1.2	57	0.01
KL28-03	48	51	0.0098		98	0.02	0.9	72	156	16	3	1	1	2.6	3.5	60	0.01
KL28-03	51	54	0.0298		298	0.01	1.2	63	199	33	4	3	5	2.8	6.6	83	0.01
KL28-03	54	56.5	0.0087		87	0.05	4.6	630	1850	15	4	2	1	1.8	10.3	13	0.01
KL28-03	56.5	59.5	0.0152		152	0.27	18.2	1000	4600	25	11	40	1	5.2	15.9	38	0.01
KL28-03	59.5	62	0.021		210	0.11	2.6	316	820	15	6	2	1	5.2	2.2	46	0.01
KL28-03	62	65	0.0124		124	0.01	1.1	145	292	33	3	0.01	1	3.1	0.0	17	0.01
KL28-03	65	68	0.0087		87	0.01	1.6	134	1720	15	12	0.01	1	4.5	1.5	26	0.01
KL28-03	68	71	0.0127		127	0.03	2.2	135	1300	8	11	0.01	1	3.2	1.8	31	0.01
KL28-03	71	74	0.014		140	0.04	1.6	156	190	7	6	0.01	1	1.1	1.2	24	0.01
KL28-03	74	77	0.0081		81	0.08	1.6	780	550	7	7	0.01	1	2.7	1.0	21	0.01
KL28-03	77	79.8	0.0114		114	0.02	2	80	170	9	8	1	1	0.9	4.1	24	0.01
KL28-03	79.8	83.5	0.0106		106	0.02	1	72	215	5	5	0.01	1	0.6	0.8	24	0.01
KL28-03	83.5	86.5	0.0084		84	0.05	0.8	60	108	2	4	0.01	1	0.6	1.6	22	0.01
KL28-03	86.5	89.5	0.0073		73	0.03	0.7	36	139	2	4	0.01	1	0.5	1.0	25	0.01
KL28-03	89.5	92.5	0.0067		67	0.02	0.1	40	103	1	3	0.01	1	0.7	0.9	21	0.01
KL28-03	92.5	95.6	0.0042		42	0.01	0.1	28	108	2	4	0.01	1	0.3	0.7	13	0.01
KL28-03	95.6	98.4	0.003		30	0.15	0.9	47	195	3	7	0.01	1	0.6	0.0	17	0.01
KL28-03	98.4	101.4	0.0033		33	0.05	0.8	39	163	2	5	0.01	1	1.5	0.7	14	0.01
KL28-03	101.4	104	0.0057		57	0.02	1.5	83	293	4	7	0.01	1	0.6	1.6	17	0.01
KL28-03	104	108	0.0039		39	0.12	1.5	66	342	3	6	0.01	1	1	2.0	17	0.01
KL28-03	108	111	0.0026		26	0.27	1.8	57	340	4	6	0.01	1	1.3	1.6	20	0.01
KL28-03	111	114	0.075		750	0.71	63	12100	16700	170	16	4	1	42	10.5	37	0.25
KL28-03	114	116.5	0.0098		98	0.46	10	1130	1650	70	12	1	4	6.9	6.7	21	0.01
KL28-03	116.5	119.7	0.014		140	0.34	7.4	740	1210	63	11	3	2	7.8	2.7	20	0.01
KL28-03	119.7	123	0.0142		142	0.38	7	1120	1410	57	12	2	2	7.7	3.0	20	0.01
KL28-03	123	126	0.004		40	0.1	6.1	760	1160	22	6	0.01	1	6	4.6	27	0.01
KL28-03	126	128.8	0.0043		43	0.03	2.7	347	860	11	5	2	1	2.5	2.5	22	0.01
KL28-03	128.8	131.8	0.0018		18	0.06	1.5	120	316	4	3	1	1	2	3.5	22	0.01
KL28-03	131.8	133.2	0.0029		29	0.1	2.2	316	640	12	14	0.01	1	5.1	2.7	32	0.01
KL28-03	133.2	135	0.0016		16	0.06	1.2	130	303	13	8	0.01	1	3	1.7	26	0.01
KL28-03	135	138	0.003		30	0.07	2.8	147	610	12	6	2	1	3.1	3.1	30	0.01
KL28-03	138	140.5	0.009		90	0.23	16.4	3320	3250	45	16	25	2	7.5	13.1	27	0.1
KL28-03	140.5	144	0.0056		56	0.24	3.2	450	460	32	5	2	3	2.3	6.0	28	0.01
KL28-03	144	147	0.0047		47	0.09	3.9	220	750	14	3	2	1	4.1	4.0	30	0.01
KL28-03	147	150	0.008		80	0.78	7.9	1210	1470	70	29	4	5	7.5	10.6	31	0.1
KL28-03	150	153	0.0054		54	0.46	5	600	710	67	19	2	3	5	5.5	57	0.01
KL28-03	153	156	0.0056		56	0.17	7	1270	1260	35	17	7	3	5.4	4.5	30	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL28-03	156	159	0.007		70	0.18	5.8	1190	1100	47	27	5	2	6.7	5.7	27	0.1
KL28-03	159	161.2	0.0054		54	0.1	5.3	870	940	24	40	6	1	5.3	5.7	34	0.11
KL28-03	161.2	164.8	0.0053		53	0.09	7.7	470	1420	22	12	9	1	4.6	6.0	40	0.01
KL28-03	164.8	167.8	0.0033		33	0.05	3.1	840	2050	12	13	2	1	3.9	2.6	27	0.01
KL28-03	167.8	171	0.0048		48	0.05	3	960	2760	12	20	2	1	3.7	3.5	16	0.01
KL28-03	171	174	0.0078		78	0.11	3	570	3240	17	32	1	1	6.2	3.5	17	0.01
KL28-03	174	177	0.0046		46	0.04	2.3	500	1280	11	30	2	2	2.6	3.7	13	0.01
KL28-03	177	180	0.0183		183	0.06	5.8	780	1540	56	43	3	1	7.7	6.7	20	0.01
KL28-03	180	183	0.0089		89	0.02	1.4	520	420	27	30	1	1	2.1	4.5	16	0.01
KL28-03	183	186	0.0197		197	0.05	5	2470	2840	33	30	4	1	5.1	5.2	16	0.11
KL28-03	186	189	0.0148		148	0.02	2.8	1850	1250	37	23	2	2	4.3	5.0	18	0.01
KL28-03	189	192	0.0165		165	0.05	2.5	3560	1600	15	23	3	1	3.3	3.5	17	0.01
KL28-03	192	195	0.0103		103	0.05	2.4	970	1220	16	17	4	1	2.4	6.5	19	0.01
KL28-03	195	198	0.0175		175	0.14	10.3	8740	5800	36	32	7	1	20	6.5	19	0.15
KL28-03	198	201	0.0238		238	0.13	12.4	5640	8400	46	61	20	1	11.8	42.3	21	0.01
KL28-03	201	204	0.0286		286	0.06	2.3	560	400	87	63	3	1	9.2	4.8	24	0.01
KL28-03	204	207	0.0189		189	0.07	11.1	6120	4300	31	27	22	3	6.7	9.6	22	0.01
KL28-03	207	210	0.0294		294	0.03	3	850	670	83	19	5	1	11.3	5.4	21	0.01
KL28-03	210	213	0.08		800	0.06	5.5	1610	1380	270	82	11	3	24	9.3	17	0.01
KL28-03	213	216	0.336		3360	0.07	9.2	2610	860	820	148	10	2	42	5.2	23	0.14
KL28-03	216	219	0.193		1930	0.12	4.3	1080	610	240	85	6	5	18	8.0	20	0.11
KL28-03	219	222.4	0.225		2250	0.28	10	11100	3250	140	38	14	3	7.9	25.0	27	2.59
KL28-03	222.4	225	0.34		3400	0.78	5.5	20700	136	380	115	9	42	5.8	41.5	133	0.25
KL28-03	225	228	0.22		2200	1.06	7.2	28400	283	73	13	52	11	7.1	29.0	62	0.47
KL28-03	228	231	1.02		10200	1.52	15.7	12200	460	210	20	81	37	6.5	63.0	169	1.66
KL28-03	231	234	1.47		14700	2.36	10.2	8440	276	100	9	49	35	3.4	55.0	125	1.34
KL28-03	234	237	1.24		12400	1.8	7.4	610	217	55	51	10	23	2.7	48.0	111	0.43
KL28-03	237	240	1.36		13600	1.45	6.2	920	356	120	48	3	43	3.5	41.8	140	0.71
KL28-03	240	243	1.31		13100	1.29	6.8	630	550	200	88	5	75	3.4	56.8	161	0.33
KL28-03	243	246	0.27		2700	0.35	2	99	99	460	280	7	66	18	69.5	328	0.13
KL28-03	246	249	0.28		2800	0.27	2.5	1370	256	420	680	6	22	4.2	36.1	282	0.13
KL28-03	249	252	2.42		24200	0.47	7	227	106	920	820	5	55	5.5	19.5	275	0.69
KL28-03	252	255.1	0.102		1020	0.56	2	870	273	180	340	10	53	5.9	52.0	270	0.73
KL28-03	255.1	258	0.24		2400	0.44	1.7	1500	244	310	307	7	70	2.4	84.0	299	0.45
KL28-03	258	261	0.86		8600	1.34	3	204	79	1270	117	2	66	2.4	20.0	216	0.72
KL28-03	261	264	0.95		9500	0.94	3.2	240	98	790	118	2	101	1.1	37.5	167	0.43
KL28-03	264	267	0.51		5100	0.72	1.9	91	47	890	273	4	83	2.3	78.0	188	0.23
KL28-03	267	270	2.15		21500	1.52	4.2	61	32	900	103	3	109	2.2	35.0	186	1.21
KL28-03	270	272.7	0.89		8900	1.07	3.2	146	52	1220	218	3	110	1.2	48.0	155	0.91
KL28-03	272.7	275.7	2.7		27000	2	6.5	64	46	1180	263	2	107	2	51.0	261	0.64
KL28-03	275.7	278.7	1.58		15800	1.25	3	140	43	120	274	2	146	1.9	46.0	197	0.21
KL28-03	278.7	281.8	2.62		26200	1.53	3.9	116	23	86	335	2	151	1.3	57.0	248	0.42
KL28-03	281.8	284.9	0.43		4300	0.71	1	62	21	90	393	4	140	1.5	63.0	173	0.1
KL28-03	284.9	287.9	0.088		880	0.28	0.1	27	14	38	420	2	52	0.8	22.5	178	0.01
KL28-03	287.9	291	0.072		720	0.24	0.7	206	56	29	442	3	83	0.8	30.9	205	0.01
KL28-03	291	294	0.0371		371	0.23	0.1	56	29	27	1080	3	98	0.8	32.0	139	0.01
KL28-03	294	297	0.078		780	0.45	2.6	1040	1620	33	250	6	45	2.1	44.3	219	0.01
KL28-03	297	300	0.73		7300	0.7	1.3	48	26	125	210	6	42	1.7	98.0	181	0.13
KL28-03	300	303	2.27		22700	1.42	3.6	87	39	86	182	6	88	1.2	31.5	228	0.18
KL28-03	303	306	2.2		22000	1.3	5.1	112	45	130	129	9	64	1.1	26.0	210	0.16
KL28-03	306	308.5	0.93		9300	1.52	4.6	150	54	180	189	19	35	1.6	19.5	257	0.1
KL28-03	308.5	311.5	1.59		15900	1.58	35	5440	1100	190	85	60	133	2.3	27.0	185	0.01
KL28-03	311.5	314	2		20000	1.61	46	25400	2850	190	31	43	195	3.7	27.0	160	0.01
KL28-03	314	317	2.38		23800	3.07	57	15800	1550	205	267	214	121	2.5	29.0	185	0.01
KL28-03	317	320.1	2.75		27500	1.45	17.1	2930	900	115	356	108	40	2.2	20.5	198	0.01
KL28-03	320.1	323.3	0.58		5800	2	52	36400	7900	220	229	186	21	14.3	20.0	166	0.01
KL28-03	323.3	326.4	0.41		4100	1.91	40	17600	9800	190	236	94	23	14.5	54.0	93	0.1
KL28-03	326.4	329.5	0.361		3610	0.72	20.9	21600	10600	120	78	38	22	12.2	85.0	45	0.13
KL28-03	329.5	332.6	0.11		1100	0.45	43	23900	26200	170	130	46	7	24	33.0	72	0.1
KL28-03	332.6	336	0.196		1960	0.47	66	53000	41600	260	225	78	5	42	37.5	28	0.13
KL28-03	336	338.8	0.0348		348	0.18	10.1	4800	5400	89	49	10	4	6.2	13.0	31	0.1
KL28-03	338.8	341.9	0.0227		227	0.13	7.8	4930	3900	57	24	6	3	6	6.6	26	0.01
KL28-03	341.9	345	0.0165		165	0.04	4.2	3250	2070	29	16	2	3	3	2.5	22	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL28-03	345	347.5	0.0105		105	0.09	3.5	1300	2200	15	11	3	2	2	3.5	19	0.01
KL28-03	347.5	363	0.291		2910	4.02	9.5	3090	2350	120	160	14	10	20	9.3	63	0.25
KL28-03	363	366	0.207		2070	1.88	31.2	19000	16500	400	349	42	8	48	28.0	112	0.27
KL28-03	366	372	0.0275		275	0.18	4	1480	660	59	73	6	3	5	5.0	26	0.01
KL28-03	372	375	0.0075		75	0.16	1	510	350	11	11	1	2	0.5	2.1	25	0.01
KL28-03	375	384	1.35		13500	0.53	31.3	15700	2570	190	610	78	16	8	14.5	29	0.32
KL28-03	384	387	0.0295		295	0.11	6.5	2200	1690	39	54	22	5	2.9	16.2	27	0.01
KL28-03	387	390.3	0.74		7400	0.32	15.2	5400	1810	550	188	42	11	26	11.7	32	0.1
KL28-03	390.3	394.7	0.0321		321	0.05	1.9	1100	550	23	20	1	3	2.8	2.7	13	0.01
KL28-03	394.7	397.7	0.0089		89	0.11	0.6	143	69	19	4	0.01	3	1.3	0.9	17	0.01
KL28-03	397.7	399.5	0.012		120	0.12	0.8	287	150	17	7	1	1	1.8	0.9	11	0.01
KL28-03	399.5	402	0.0101		101	0.03	0.1	174	66	11	11	0.01	2	2	1.2	13	0.01
KL28-03	402	405	0.0157		157	0.3	6.7	440	1070	16	13	32	1	75	14.5	19	0.01
KL28-03	405	408	0.094		940	0.33	12.1	2120	251	240	66	5	5	36	5.7	25	0.01
KL28-03	408	411	0.0326		326	0.77	2.7	700	206	63	28	2	2	38	5.5	26	0.01
KL28-03	411	414	0.0266		266	0.41	3.1	750	276	39	24	5	3	30	3.8	21	0.01
KL28-03	414	418.5	0.095		950	0.39	13.2	2560	410	230	70	7	5	48	3.5	21	0.01
KL28-03	418.5	421.6	0.0095		95	0.04	0.7	154	50	11	13	0.01	1	1.6	1.2	12	0.01
KL28-03	421.6	424.7	0.0028		28	0.1	0.1	47	40	19	4	0.01	4	2.7	1.2	20	0.01
KL28-03	424.7	427.8	0.0089		89	0.07	0.1	136	87	15	4	1	1	1.2	1.5	14	0.01
KL28-03	427.8	430.5	0.0025		25	0.02	0.1	24	15	18	3	0.01	1	1	0.0	16	0.01
KL28-03	430.5	433	0.0016		16	0.02	0.1	27	18	15	2	0.01	1	0.6	1.2	24	0.01
KL28-04	0	3	0.0052		52	0.01	0.1	54	28	6	1	0.01	1	0.4	0.0	18	0.01
KL28-04	3	6	0.0044		44	0.01	0.5	201	102	6	1	0.01	1	1	0.9	20	0.01
KL28-04	6	9	0.0178		178	0.01	0.1	122	78	7	4	0.01	2	1.1	2.0	24	0.01
KL28-04	9	12	0.0023		23	0.03	0.1	174	192	17	1	0.01	2	1	1.7	18	0.01
KL28-04	12	15	0.002		20	0.01	0.1	39	36	5	1	0.01	3	0.4	0.7	25	0.01
KL28-04	15	18	0.0008		8	0.01	0.1	29	25	4	1	0.01	1	0.01	0.8	21	0.01
KL28-04	18	21	0.0045		45	0.01	0.1	27	32	6	1	0.01	1	0.7	4.4	21	0.01
KL28-04	21	24	0.0006		6	0.01	0.1	40	16	6	1	0.01	1	0.5	1.1	32	0.01
KL28-04	24	27	0.0012		12	0.01	0.1	50	30	8	1	0.01	1	0.5	1.2	30	0.01
KL28-04	27	30	0.0015		15	0.01	0.1	42	18	5	1	0.01	1	0.01	1.4	30	0.01
KL28-04	30	33	0.0017		17	0.01	0.1	44	23	4	1	0.01	1	0.01	1.6	25	0.01
KL28-04	33	36	0.0051		51	0.01	0.1	79	45	3	1	0.01	1	0.3	1.8	20	0.01
KL28-04	36	39	0.002		20	0.44	2.2	107	206	38	1	1	1	16.2	3.5	77	0.01
KL28-04	39	42	0.0067		67	0.39	2.6	159	251	36	1	5	1	9.2	10.7	63	0.01
KL28-04	42	48	0.08		800	0.3	47	1430	3590	250	5	150	6	14.1	68.0	57	0.01
KL28-04	48	50.5	0.0038		38	0.11	1.6	164	640	21	2	3	1	2.4	2.9	36	0.01
KL28-04	50.5	53.5	0.006		60	0.12	3.2	247	1110	21	8	5	1	3.4	1.3	67	0.01
KL28-04	53.5	56.5	0.0016		16	0.09	6.7	109	1400	9	6	9	1	3.8	4.7	54	0.01
KL28-04	56.5	63	0.004		40	0.13	2.8	111	1140	17	5	2	1	2.9	1.8	165	0.01
KL28-04	63	66	0.0022		22	0.01	0.9	153	300	18	1	1	1	2.8	0.6	31	0.01
KL28-04	66	69	0.0042		42	0.02	1.2	198	600	10	1	3	1	2.3	1.2	37	0.01
KL28-04	69	70.5	0.0013		13	0.01	0.7	88	314	4	1	0.01	2	2	0.8	30	0.01
KL28-04	70.5	73.5	0.0013		13	0.01	1.4	140	660	11	3	1	1	3.3	0.8	28	0.01
KL28-04	73.5	76.5	0.0031		31	0.01	1.3	205	610	9	8	2	1	2.8	0.6	26	0.01
KL28-04	76.5	77.7	0.0024		24	0.01	0.9	59	410	7	5	2	1	1	0.7	41	0.01
KL28-04	77.7	80.1	0.0176		176	0.01	0.7	73	143	14	4	0.01	1	2.4	0.8	14	0.01
KL28-04	80.1	82.5	0.0011		11	0.01	0.1	33	79	6	3	0.01	1	0.5	0.7	14	0.01
KL28-04	82.5	85.5	0.0012		12	0.01	0.9	102	150	12	4	0.01	1	2.1	0.6	25	0.01
KL28-04	85.5	88.5	0.0023		23	0.02	1.6	331	730	3	5	0.01	2	2.6	1.9	21	0.01
KL28-04	88.5	91.5	0.001		10	0.01	1.3	130	293	2	4	0.01	1	3	1.6	17	0.01
KL28-04	91.5	94.5	0.0023		23	0.01	2.6	580	680	3	3	0.01	1	1.7	3.3	15	0.01
KL28-04	94.5	97.3	0.002		20	0.01	3.2	500	1050	1	3	0.01	1	2.6	2.9	15	0.01
KL28-04	97.3	100.4	0.0013		13	0.01	3.6	357	780	2	2	3	1	2.6	3.1	17	0.01
KL28-04	100.4	103	0.003		30	0.03	6.6	480	1110	4	1	3	1	1.8	4.2	16	0.01
KL28-04	103	105.4	0.0094		94	0.07	16.7	890	1860	22	2	4	1	6.3	15.3	16	0.01
KL28-04	105.4	107.4	0.0046		46	0.03	10.7	330	1870	9	1	13	1	5.3	8.6	15	0.01
KL28-04	107.4	110.3	0.0024		24	0.04	8.4	63	1340	6	1	13	1	3.9	4.3	17	0.01
KL28-04	110.3	113.5	0.0015		15	0.03	3.2	46	372	5	1	4	1	2	2.2	20	0.01
KL28-04	113.5	115.8	0.0018		18	0.02	1.4	99	190	3	1	2	1	1.7	1.7	18	0.01
KL28-04	115.8	117.4	0.0025		25	0.01	0.7	33	71	2	1	0.01	1	1.5	0.8	22	0.01
KL28-04	117.4	119.5	0.0034		34	0.01	1.6	169	196	2	1	1	1	1.2	1.3	21	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL28-04	119.5	122.5	0.0022		22	0.01	1.9	43	181	3	1	2	3	1.5	1.6	20	0.01
KL28-04	122.5	125.6	0.0032		32	0.01	1.2	430	730	5	40	0.01	1	2.6	2.1	23	0.01
KL28-04	125.6	128.1	0.0017		17	0.01	1.6	181	362	3	4	0.01	1	1.3	1.8	22	0.01
KL28-04	128.1	131.5	0.0016		16	0.01	0.9	241	580	0.01	3	0.01	1	0.7	1.1	19	0.01
KL28-04	131.5	134.6	0.0019		19	0.01	1.3	320	470	2	4	0.01	1	1.1	1.2	19	0.01
KL28-04	134.6	137.2	0.0012		12	0.01	1.4	110	275	0.01	7	0.01	1	0.9	1.1	17	0.01
KL28-04	137.2	139.5	0.0011		11	0.01	1.7	400	358	7	9	0.01	1	0.8	1.3	15	0.01
KL28-04	139.5	142.4	0.0012		12	0.01	1.1	247	372	3	9	0.01	1	0.7	0.7	9	0.01
KL28-04	142.4	144.9	0.0011		11	0.01	2	940	530	3	3	0.01	1	1.2	0.8	11	0.01
KL28-04	144.9	147.3	0.001		10	0.01	1	361	490	0.01	3	0.01	1	0.6	0.0	10	0.01
KL28-04	147.3	149.6	0.001		10	0.01	0.7	273	301	0.01	7	0.01	1	0.7	0.0	9	0.01
KL28-04	149.6	152	0.0015		15	0.01	2.8	1480	1860	2	5	0.01	1	1.9	1.1	10	0.01
KL28-04	152	154.5	0.002		20	0.03	6.3	2880	2910	6	3	0.01	1	4.1	2.6	9	0.01
KL28-04	154.5	156	0.0012		12	0.02	2.4	440	780	2	3	0.01	1	1.3	1.0	12	0.01
KL28-04	156	158.4	0.019		190	0.06	13.9	1430	2900	15	18	0.01	3	7.3	0.7	16	0.01
KL28-04	158.4	161.6	0.0049		49	0.09	24.3	1550	4680	20	28	1	1	4.6	5.8	11	0.01
KL28-04	161.6	163.5	0.003		30	0.04	3.7	590	1510	8	12	0.01	1	1.8	3.1	14	0.01
KL28-04	163.5	166.4	0.0014		14	0.03	2.6	460	1780	5	5	0.01	1	1.3	1.1	16	0.01
KL28-04	166.4	169.5	0.0018		18	0.03	6.6	520	1150	7	7	0.01	1	2	2.2	14	0.01
KL28-04	169.5	173	0.0048		48	0.11	17.2	6500	12500	20	5	1	1	19.3	2.4	15	0.16
KL28-04	173	175.5	0.0044		44	0.17	10.3	4600	5300	19	39	0.01	1	10.3	3.3	19	0.2
KL28-04	175.5	178.5	0.0037		37	0.12	5.5	1780	2390	17	52	0.01	1	4.1	2.3	21	0.11
KL28-04	178.5	181.5	0.006		60	0.11	6.8	2650	2960	27	47	0.01	1	3.2	6.6	18	0.2
KL28-04	181.5	184.5	0.0067		67	0.04	6.9	1300	2490	27	29	0.01	1	3.3	3.8	18	0.01
KL28-04	184.5	186	0.0028		28	0.03	3.1	630	1400	13	31	0.01	1	1.2	1.1	15	0.01
KL28-04	186	189	0.0092		92	0.07	7.8	4300	5360	15	22	0.01	1	8.1	11.5	20	0.01
KL28-04	189	192	0.0091		91	0.07	6.1	2460	3870	44	49	0.01	1	4.2	4.7	28	0.01
KL28-04	192	195	0.014		140	0.15	11.4	6600	5200	35	35	4	1	8.6	11.6	21	0.01
KL28-04	195	198	0.003		30	0.07	1.5	276	700	26	14	1	1	1.6	2.3	18	0.01
KL28-04	198	200.8	0.0035		35	0.01	2.1	1030	1790	6	5	0.01	1	3.2	0.0	13	0.01
KL28-04	200.8	203.9	0.0043		43	0.02	5.2	2620	3640	6	4	0.01	1	4.8	0.7	12	0.01
KL28-04	203.9	205.5	0.004		40	0.02	3.8	1800	3460	2	7	0.01	1	6	3.3	13	0.01
KL28-04	205.5	208.5	0.0284		284	0.14	12.9	16400	7000	39	12	22	4	8.2	16.9	24	0.01
KL28-04	208.5	211.5	0.017		170	0.08	11.3	8300	7900	28	23	10	1	12.1	10.3	18	0.01
KL28-04	211.5	214.5	0.014		140	0.08	10.9	4600	7600	31	30	14	1	7.8	9.3	17	0.01
KL28-04	214.5	217.5	0.0214		214	0.07	9.2	4190	4380	41	107	15	1	2.9	4.7	16	0.01
KL28-04	217.5	219	0.0089		89	0.04	2.5	1500	1640	20	48	8	1	2	4.2	12	0.01
KL28-04	219	220.9	0.0129		129	0.13	2.4	1230	1210	35	43	9	1	1.6	0.7	15	0.01
KL28-04	220.9	222	0.292		2920	0.98	16.4	2760	2070	1020	220	86	10	14.3	2.2	43	0.39
KL28-04	222	224.7	0.081		810	0.15	2.6	1070	1010	150	48	25	1	8.3	2.2	158	0.01
KL28-04	224.7	226.2	0.0186		186	0.04	0.7	89	48	13	399	7	1	1.6	0.0	67	0.01
KL28-04	226.2	228.8	0.103		1030	0.11	2.2	1000	189	12	1270	163	3	1.1	3.4	121	0.01
KL28-04	228.8	230.5	0.29		2900	0.21	5.6	8300	365	24	700	274	16	1.3	8.9	24	0.01
KL28-04	230.5	232.1	0.041		410	0.12	0.9	840	580	110	21	3	1	2.6	3.3	9	0.01
KL28-04	232.1	235.1	0.0381		381	1.67	1.8	1680	620	91	193	10	1	4	4.5	25	0.01
KL28-04	235.1	238.3	0.0297		297	0.06	2.4	1660	1000	25	610	12	1	0.5	6.6	44	0.01
KL28-04	238.3	240.4	0.214		2140	0.54	3.8	860	98	66	103	18	6	2.4	17.3	25	0.01
KL28-04	240.4	243	0.432		4320	0.41	9.1	1890	580	29	1970	23	12	0.4	4.6	14	0.01
KL28-04	243	246	0.62		6200	0.76	52	25200	9600	73	610	180	27	0.3	12.3	52	0.01
KL28-04	246	249	0.46		4600	0.51	16.6	12800	730	60	96	98	9	0.4	16.8	28	0.01
KL28-04	249	252	0.42		4200	0.83	8.9	34600	61	64	158	66	10	0.4	11.7	22	0.01
KL28-04	252	255	1.35		13500	4.59	11.6	12500	27	54	35	107	19	0.6	4.4	95	0.01
KL28-04	255	258	0.79		7900	1.93	4.5	138	13	32	267	26	18	0.5	7.8	45	0.01
KL28-04	258	261	0.151		1510	0.7	1.2	67	12	31	720	4	14	0.3	8.9	33	0.01
KL28-04	261	262.5	0.19		1900	1.9	1.4	101	20	48	720	5	12	1	8.4	37	0.01
KL28-04	262.5	265.2	2.52		25200	13.8	14.7	700	42	43	208	61	83	2	17.0	44	0.01
KL28-04	265.2	267	0.84		8400	2.05	4.5	480	43	10	105	4	107	1	31.6	133	0.01
KL28-04	267	270	1.71		17100	2.46	8.2	920	97	32	94	6	80	2.4	37.5	122	0.01
KL28-04	270	273	1.88		18800	2.35	11.3	500	192	24	10	7	58	2.9	27.0	28	0.01
KL28-04	273	276	2.04		20400	2.31	10.2	490	62	13	10	4	87	1.1	24.5	116	0.01
KL28-04	276	278.2	1.87		18700	1.5	4.5	180	29	12	3	3	437	0.7	31.0	165	0.01
KL28-04	278.2	280	2.13		21300	1.78	3.9	339	36	5	230	0.01	138	0.01	9.0	58	0.01
KL28-04	280	282	4.02		40200	2.73	6.1	315	29	6	271	0.01	90	0.01	9.0	50	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL28-04	282	285	4.85	48500	3.85	6.8	231	23	11	655	0.01	113	0.01	7.0	57	0.01
KL28-04	285	288	3.62	36200	2.59	4.1	420	133	10	53	0.01	68	0.9	11.5	25	0.01
KL28-04	288	291	3.44	34400	2.17	2.8	202	37	3	270	0.01	83	0.01	11.0	24	0.01
KL28-04	291	294	3.36	33600	2.09	2.4	231	24	5	680	0.01	63	0.3	12.0	60	0.01
KL28-04	294	297	4.46	44600	2.14	4.3	381	34	180	1130	0.01	72	4.2	14.0	68	0.18
KL28-04	297	298.9	1.42	14200	1.11	1.8	229	11	3	810	1	56	0.01	8.5	37	0.01
KL28-04	298.9	300.8	14.45	144500	6.49	7	520	30	3	2260	0.01	139	0.01	16.2	54	0.01
KL28-04	300.8	303	3.78	37800	2.07	3.1	118	16	4	950	0.01	65	0.01	19.0	160	0.01
KL28-04	303	306	5.8	58000	2.19	9.5	209	85	190	2180	0.01	55	2.6	20.0	271	0.18
KL28-04	306	309	4.07	40700	0.65	7.5	490	100	160	980	0.01	28	2.5	14.0	157	0.29
KL28-04	309	312	3.88	38800	0.78	7.3	630	183	310	740	0.01	33	26	21.0	158	0.33
KL28-04	312	315	2.8	28000	0.34	3.5	1310	294	130	1600	0.01	25	0.5	23.0	205	0.45
KL28-04	315	318	1.63	16300	0.23	2.2	710	128	240	890	0.01	16	0.9	14.5	71	0.36
KL28-04	318	321	1.66	16600	0.22	2.1	650	207	540	600	0.01	22	5.8	13.5	65	0.51
KL28-04	321	324	1.74	17400	0.26	1.7	118	58	51	800	0.01	24	1.2	12.5	55	0.21
KL28-04	324	327	1.67	16700	0.34	1.5	75	24	30	625	0.01	33	0.2	12.0	51	0.13
KL28-04	327	329.4	1.12	11200	0.3	1	104	35	47	680	0.01	32	0.4	13.0	240	0.1
KL28-04	329.4	332.5	1.19	11900	0.26	1	126	22	51	1065	1	31	0.01	13.5	71	0.01
KL28-04	332.5	335.5	0.54	5400	0.23	1.3	68	8	2	458	0.01	18	0.01	10.3	36	0.01
KL28-04	335.5	338.6	1.13	11300	0.41	1.2	178	66	11	600	0.01	36	0.5	11.2	151	0.01
KL28-04	338.6	341.7	1.6	16000	0.49	1.6	216	67	160	500	0.01	32	0.9	15.4	65	0.1
KL28-04	341.7	344.8	1.19	11900	0.49	1.4	420	104	24	575	0.01	24	1	10.5	241	0.17
KL28-04	344.8	347.9	0.97	9700	0.55	1.1	121	59	2	324	0.01	17	0.01	9.7	77	0.01
KL28-04	347.9	351	1.17	11700	0.33	1.4	1320	660	7	367	0.01	17	0.01	12.5	57	0.22
KL28-04	351	354	1.06	10600	0.4	1.2	264	57	14	205	0.01	16	0.01	14.5	57	0.11
KL28-04	354	357	1.18	11800	0.69	1.3	130	66	30	620	0.01	12	0.3	14.0	67	0.01
KL28-04	357	360	1	10000	0.51	1.2	129	32	19	182	0.01	13	0.3	11.7	225	0.01
KL28-04	360	363	1.12	11200	0.61	1.9	570	184	60	370	0.01	19	0.2	7.3	100	0.11
KL28-04	363	366	1.44	14400	0.83	2	62	30	5	422	0.01	23	0.2	9.5	97	0.01
KL28-04	366	369	1.15	11500	0.54	1.6	89	19	3	950	1	26	0.3	9.0	55	0.01
KL28-04	369	372	1.58	15800	0.95	2.6	147	174	19	510	1	28	0.01	16.0	106	0.01
KL28-04	372	375	1.4	14000	0.98	54	85	263	21	340	3	23	0.01	14.0	54	0.01
KL28-04	375	378	2.61	26100	0.56	3.6	49	84	290	230	0.01	18	0.9	20.0	158	0.01
KL28-04	378	381	1.1	11000	0.53	1.5	209	167	29	381	0.01	31	0.2	8.4	136	0.01
KL28-04	381	384	1.35	13500	0.9	2.3	169	101	18	245	0.01	27	0.4	16.5	52	0.01
KL28-04	384	387	1.33	13300	0.5	2.2	430	710	55	500	0.01	27	0.6	15.0	114	0.01
KL28-04	387	390	1.18	11800	0.4	1.8	1190	580	340	362	1	40	0.7	8.2	125	0.24
KL28-04	390	391.8	1.87	18700	0.48	2.4	680	134	66	338	0.01	31	0.4	14.5	116	0.4
KL28-04	391.8	393.2	1.62	16200	0.39	1.9	349	183	140	59	0.01	18	0.2	9.5	123	0.15
KL28-04	393.2	396	0.62	6200	0.27	1.6	76	7	5	41	0.01	16	0.3	5.8	86	0.01
KL28-04	396	399	3.88	38800	1.05	3.5	223	57	260	1130	1	34	3.8	14.5	139	0.12
KL28-04	399	402	3.48	34800	1.61	3.9	160	44	28	1000	0.01	44	0.01	18.0	56	0.01
KL28-04	402	405	2.59	25900	0.64	2.7	176	79	45	684	1	37	0.6	9.5	218	0.01
KL28-04	405	408	2.55	25500	1.03	2.5	122	54	45	160	0.01	37	0.01	13.5	183	0.01
KL28-04	408	411	2.31	23100	0.96	2.7	750	105	49	226	0.01	40	0.5	17.5	115	0.14
KL28-04	411	414	1.92	19200	0.32	8.7	2600	1560	3200	610	0.01	18	160	7.8	108	0.65
KL28-04	414	417	1.05	10500	0.26	3.2	1680	620	1150	378	0.01	10	19.3	6.1	237	0.46
KL28-04	417	420	1.49	14900	0.81	11.3	1730	1110	3500	657	0.01	14	270	14.5	227	0.8
KL28-04	420	423	1.46	14600	0.36	2.5	265	231	1140	384	0.01	12	20	7.4	231	0.01
KL28-04	423	426	1.03	10300	0.31	3	920	307	2160	281	0.01	12	40	7.4	230	0.31
KL28-04	426	429	1.42	14200	0.44	3.1	1800	3400	1830	306	0.01	15	42	12.0	76	0.61
KL28-04	429	432	2.2	22000	0.56	2.6	840	1510	220	331	0.01	34	5.8	15.0	77	0.22
KL28-04	432	435	3.1	31000	1.57	4.6	730	480	76	1510	0.01	78	1.6	26.0	148	0.01
KL28-04	435	438	3.42	34200	2.21	8.7	700	203	24	320	1	166	1.1	35.0	176	0.01
KL28-04	438	441	5.07	50700	2.3	12.1	363	14	4	182	0.01	75	0.01	14.0	104	0.01
KL28-04	441	444	2.55	25500	1.65	7.1	6500	7300	1040	272	0.01	72	2.8	15.5	145	0.28
KL28-04	444	447	2.6	26000	2.23	9.6	2400	3100	140	180	1	136	6.6	16.5	127	0.01
KL28-04	447	450	2.74	27400	2.98	11	19400	15900	780	160	0.01	63	28	21.0	143	0.25
KL28-04	450	453	3.96	39600	1.58	11.5	1530	112	6	390	0.01	105	0.4	22.0	62	0.01
KL28-04	453	456	2.07	20700	1.1	9.6	4100	700	24	160	2	52	0.7	14.8	99	0.01
KL28-04	456	459	2.56	25600	1.69	10.2	570	16	6	9	67	38	0.5	18.0	90	0.01
KL28-04	459	462	1.86	18600	1.3	11	740	21	3	20	3	37	0.3	19.0	48	0.01
KL28-04	462	465	1.81	18100	1.31	8.6	490	30	11	11	3	38	0.01	19.0	87	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL28-04	465	468	2.51	25100	2.51	10.5	570	17	27	29	3	39	0.2	20.0	76	0.01
KL28-04	468	471	2.53	25300	1.94	9.9	690	34	42	21	2	49	0.6	19.5	74	0.01
KL28-04	471	474	3.49	34900	1.95	10.2	2500	242	62	17	0.01	72	0.7	32.0	20	0.01
KL28-04	474	477	3.57	35700	2.43	13.8	1230	80	14	26	2	43	0.8	25.0	39	0.01
KL28-04	477	480	1.49	14900	1.39	5.3	415	15	24	476	2	42	1.7	20.5	69	0.01
KL28-04	480	483	1.82	18200	1.39	9.7	1380	13	19	5	6	63	0.4	16.2	33	0.01
KL28-04	483	486	2.3	23000	2.79	18.2	2500	14	30	4	6	52	0.3	18.5	17	0.01
KL28-04	486	489	1.63	16300	1.02	6.8	640	7	21	40	3	53	0.2	31.0	63	0.01
KL28-04	489	492	1.49	14900	1.06	11.1	1240	8	13	56	8	56	0.2	26.0	31	0.01
KL28-04	492	495	2.15	21500	1.58	18.1	1030	12	21	32	5	59	0.5	17.5	16	0.01
KL28-04	495	498	1.56	15600	1.55	7.9	430	14	13	57	3	50	0.01	19.5	35	0.01
KL28-04	498	501	2.34	23400	2.16	9.8	730	8	2	18	4	71	0.01	10.0	110	0.01
KL28-04	501	504	1.26	12600	0.63	3.6	161	7	5	36	3	67	0.01	20.5	128	0.01
KL28-04	504	507	1.19	11900	0.83	4	241	7	10	122	2	77	0.01	19.8	207	0.01
KL28-04	507	510	1.28	12800	0.8	3.8	227	6	6	120	0.01	34	0.01	9.5	90	0.01
KL28-04	510	513	0.38	3800	0.11	1.8	85	21	6	45	0.01	11	0.01	5.6	83	0.01
KL28-04	513	516	0.7	7000	0.45	2.3	125	6	13	162	0.01	17	3.7	6.3	61	0.01
KL28-04	516	519	1.53	15300	0.55	3.1	121	18	11	139	0.01	30	0.01	10.5	105	0.01
KL28-04	519	522	1.5	15000	0.66	3.4	124	5	3	93	0.01	24	0.01	9.2	78	0.01
KL28-04	522	525	1.96	19600	0.73	4	149	6	5	256	0.01	31	0.01	12.0	74	0.01
KL28-04	525	528	0.75	7500	0.49	2.5	154	10	1	21	0.01	21	0.01	6.8	38	0.01
KL28-04	528	531	0.52	5200	0.15	0.9	58	8	1	138	0.01	20	0.01	9.5	50	0.01
KL28-04	531	534	0.91	9100	0.82	3.2	112	8	0.01	130	0.01	18	0.01	11.1	42	0.01
KL28-04	534	537	0.83	8300	0.32	1.8	118	56	12	205	0.01	17	0.8	6.5	30	0.01
KL28-04	537	540	0.51	5100	0.16	1.2	61	12	2	28	0.01	15	0.4	8.7	23	0.01
KL28-04	540	543	0.163	1630	0.05	0.6	45	11	4	70	0.01	8	0.01	3.0	40	0.01
KL28-04	543	546	0.65	6500	0.18	3.1	93	15	2	60	0.01	9	0.2	5.0	22	0.01
KL28-04	546	549	0.53	5300	0.29	1.7	200	11	4	118	0.01	26	10.5	7.3	61	0.01
KL28-04	549	552	0.32	3200	0.11	1.5	60	15	2	27	0.01	9	0.3	6.0	53	0.01
KL28-04	552	555	0.71	7100	0.29	2	66	7	3	59	0.01	17	0.2	3.5	54	0.01
KL28-04	555	558	0.42	4200	0.12	1	58	8	1	60	0.01	12	0.01	3.3	88	0.01
KL28-04	558	561	0.32	3200	0.09	1.8	66	8	1	353	0.01	11	0.01	3.8	86	0.01
KL28-04	561	563.5	0.43	4300	0.27	1	56	7	0.01	103	0.01	12	0.01	4.5	61	0.01
KL28-04	563.5	566.6	0.44	4400	0.12	1.3	46	6	0.01	62	0.01	13	0.01	5.3	64	0.01
KL28-04	566.6	569.7	0.53	5300	0.26	1.3	61	7	0.01	136	0.01	21	0.01	6.0	69	0.01
KL28-04	569.7	572.8	0.33	3300	0.15	1.1	59	7	1	55	0.01	14	0.01	6.2	44	0.01
KL28-04	572.8	575.9	0.27	2700	0.11	1	53	7	3	56	0.01	13	0.3	8.0	45	0.01
KL28-04	575.9	579	1.53	15300	0.4	1.9	387	251	66	570	1	30	0.5	15.5	66	0.13
KL28-04	579	582	0.49	4900	0.19	1.7	61	8	0.01	106	0.01	17	0.01	6.5	36	0.01
KL28-04	582	585.5	0.59	5900	0.18	3.2	120	12	0.01	59	0.01	12	0.2	10.1	103	0.01
KL28-04	585.5	588.5	0.41	4100	0.23	1.4	116	90	0.01	35	0.01	14	0.2	6.2	48	0.01
KL28-04	588.5	591.6	0.82	8200	0.35	3.1	121	43	3	24	0.01	25	1.2	8.0	32	0.01
KL28-04	591.6	594	0.43	4300	0.1	1.2	32	7	0.01	64	0.01	11	0.01	4.8	36	0.01
KL28-04	594	597	0.48	4800	0.14	1.3	38	7	1	65	0.01	9	0.2	5.1	193	0.01
KL28-04	597	600	0.52	5200	0.15	1.5	48	9	0.01	55	0.01	15	0.3	5.7	32	0.01
KL28-04	600	603	0.91	9100	0.2	1.1	55	12	7	184	0.01	10	0.2	6.5	158	0.21
KL28-04	603	606	0.5	5000	0.13	0.6	29	9	0.01	106	0.01	8	0.2	6.3	306	0.01
KL28-04	606	609	0.83	8300	0.2	1.2	107	28	37	232	1	8	0.4	7.0	270	0.01
KL28-04	609	612	0.52	5200	0.19	1.7	73	17	42	640	0.01	9	0.4	2.5	243	0.01
KL28-04	612	615	0.37	3700	0.11	1.6	63	20	40	490	0.01	7	1.2	4.8	43	0.01
KL28-04	615	618	0.46	4600	0.08	1.7	57	7	0.01	146	0.01	6	0.01	3.5	12	0.01
KL28-04	618	621	0.436	4360	0.09	1.6	57	7	0.01	136	0.01	8	0.01	4.3	50	0.01
KL28-04	621	624	0.4	4000	0.08	1.2	71	21	0.01	316	0.01	7	0.3	3.3	74	0.01
KL28-04	624	627	0.59	5900	0.22	1.9	55	10	0.01	425	0.01	17	0.01	6.0	20	0.01
KL28-04	627	630	0.5	5000	0.18	1.3	75	32	1	181	0.01	8	0.3	5.3	25	0.01
KL28-04	630	633	0.22	2200	0.06	0.9	29	7	1	286	0.01	5	0.2	2.8	20	0.01
KL28-04	633	636	1.3	13000	0.33	2.2	54	8	2	104	0.01	31	0.2	21.0	28	0.01
KL28-04	636	639	1.27	12700	0.36	2.4	89	24	0.01	610	0.01	34	1.2	15.0	40	0.01
KL28-04	639	642	1.96	19600	0.8	4.2	121	9	3	68	0.01	39	0.7	20.0	45	0.01
KL28-04	642	645	1.58	15800	0.61	3.2	80	8	9	305	0.01	41	0.9	24.0	81	0.01
KL28-04	645	648	0.7	7000	0.35	1.7	81	9	6	32	0.01	22	0.3	11.0	62	0.01
KL28-04	648	651	1.2	12000	0.49	3.1	131	10	1	94	0.01	40	0.4	16.0	69	0.01
KL28-04	651	654	3.38	33800	1.12	6.6	404	228	640	1275	1	34	6.6	16.0	167	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL28-04	654	657	1.94	19400	0.72	5.4	156	12	12	120	0.01	29	0.01	10.8	70	0.01
KL28-04	657	660	1.32	13200	0.54	3.1	170	14	2	89	0.01	26	1.2	2.5	54	0.01
KL28-04	660	663	0.59	5900	0.36	2.1	100	13	3	27	2	24	4.1	6.0	65	0.01
KL28-04	663	666	0.85	8500	0.37	2.5	102	11	3	26	1	28	0.9	8.5	33	0.01
KL28-04	666	669	0.491	4910	0.2	1	73	11	9	71	0.01	14	5.2	8.0	41	0.01
KL28-04	669	672	0.93	9300	0.48	2.7	160	10	3	43	0.01	13	0.9	8.8	34	0.01
KL28-04	672	675	0.81	8100	0.39	2.6	145	10	4	36	0.01	21	0.6	13.3	38	0.01
KL28-04	675	678	0.64	6400	0.31	1.6	130	11	4	26	0.01	25	0.3	12.5	39	0.01
KL28-04	678	681	1.15	11500	0.59	3.1	120	8	4	31	0.01	23	1.2	12.8	45	0.01
KL28-04	681	684	1.84	18400	0.6	5.1	266	9	3	38	0.01	29	0.01	14.0	38	0.01
KL28-04	684	686.8	1.2	12000	0.44	3	125	9	2	49	0.01	21	0.01	8.5	30	0.01
KL28-04	686.8	689.8	1.26	12600	0.55	3.3	110	8	4	93	0.01	15	0.2	10.5	40	0.01
KL28-04	689.8	692.9	1.99	19900	0.71	5.1	148	7	4	62	0.01	40	0.01	12.5	58	0.01
KL28-04	692.9	696	1.33	13300	0.41	3.5	114	9	2	89	0.01	20	0.01	10.0	21	0.01
KL28-04	696	699	1.06	10600	0.42	2.7	90	15	4	180	0.01	21	0.01	7.8	40	0.01
KL28-04	699	702	0.75	7500	0.36	2.2	91	10	3	68	0.01	14	0.01	6.5	19	0.01
KL28-04	702	705	0.86	8600	0.37	2.4	83	10	6	55	0.01	13	0.01	7.8	29	0.01
KL28-04	705	708	1.15	11500	0.51	2.5	82	7	2	13	0.01	14	0.01	9.3	18	0.01
KL28-04	708	711	0.82	8200	0.31	2.1	88	10	3	21	0.01	17	0.01	10.0	32	0.01
KL28-04	711	714	0.66	6600	0.41	1.7	109	12	4	69	0.01	23	0.01	6.5	38	0.01
KL28-04	714	717	0.86	8600	0.28	1.5	68	8	3	101	0.01	12	0.01	7.8	19	0.01
KL28-04	717	720	0.8	8000	0.27	1.6	71	11	0.01	31	0.01	16	0.01	10.3	21	0.01
KL28-04	720	723	1.24	12400	0.32	2.2	78	11	3	76	0.01	17	0.01	5.5	30	0.01
KL28-04	723	726	1.06	10600	0.31	2.1	80	15	1	40	0.01	14	0.01	7.8	17	0.01
KL28-04	726	729	1.18	11800	0.32	2.4	91	10	1	17	0.01	20	0.01	10.0	14	0.01
KL28-04	729	732	1.17	11700	0.32	1.9	87	9	1	11	0.01	14	0.01	5.5	21	0.01
KL28-04	732	735	1.08	10800	0.3	2.3	90	12	2	60	0.01	15	0.2	10.5	29	0.01
KL28-04	735	738	0.775	7750	0.23	1.3	62	6	0.01	63	0.01	15	0.01	9.4	21	0.01
KL28-04	738	741	0.86	8600	0.28	1.5	73	6	1	19	0.01	11	0.01	6.8	19	0.01
KL28-04	741	744	0.7	7000	0.23	1.5	104	8	3	36	0.01	16	0.01	6.8	30	0.01
KL28-04	744	747	1.07	10700	0.27	1.7	110	11	1	58	0.01	13	0.01	7.0	20	0.01
KL28-04	747	750	1.12	11200	0.3	2	114	9	2	140	0.01	17	0.01	13.0	16	0.01
KL28-04	750	753	0.97	9700	0.26	1.4	72	7	0.01	33	0.01	15	0.01	6.4	28	0.01
KL28-04	753	756	1.47	14700	0.48	1.8	116	16	0.01	31	0.01	21	0.01	13.5	29	0.01
KL28-04	756	759	1.76	17600	0.39	3.1	140	13	1	40	0.01	25	0.01	15.5	25	0.01
KL28-04	759	762	1.24	12400	0.41	2.4	121	11	1	13	0.01	16	0.01	10.5	27	0.01
KL28-04	762	765	0.228	2280	0.11	0.6	100	16	0.01	30	0.01	13	1.8	2.4	41	0.01
KL28-04	765	768	0.41	4100	0.17	1	120	10	0.01	22	0.01	16	28	4.0	19	0.01
KL28-04	768	771	1.13	11300	0.29	2	100	10	0.01	31	0.01	15	0.2	12.8	32	0.01
KL28-04	771	774	1.9	19000	0.4	4.4	134	13	2	50	0.01	22	0.5	11.0	22	0.01
KL28-04	774	777	1.17	11700	0.51	3.2	80	8	1	140	0.01	16	0.2	12.5	14	0.01
KL28-04	777	780	0.67	6700	0.2	2.1	100	11	0.01	25	0.01	9	0.2	6.3	16	0.01
KL28-04	780	781.8	1.58	15800	0.32	5.4	380	56	2	13	0.01	18	0.2	12.5	21	0.01
KL28-04	781.8	784.6	0.83	8300	0.27	2.8	101	10	1	219	0.01	14	0.01	9.3	26	0.01
KL28-04	784.6	787.2	1.01	10100	0.33	3.3	141	14	1	19	0.01	30	0.2	13.5	27	0.01
KL28-04	787.2	789	0.75	7500	0.21	2.1	244	62	2	18	0.01	36	0.01	11.8	48	0.01
KL28-04	789	792	0.74	7400	0.16	1.9	128	16	10	80	0.01	24	0.01	22.4	23	0.01
KL28-04	792	793.5	0.6	6000	0.18	1.4	86	13	3	16	0.01	31	0.01	21.3	24	0.01
KL28-04	793.5	796.3	0.83	8300	0.22	2.3	83	8	3	27	0.01	21	0.01	12.3	18	0.01
KL28-04	796.3	798	0.068	680	0.01	0.1	9	1	0.01	97	0.01	1	0.01	1.0	0	0.01
KL28-04	798	799.8	0.2	2000	0.02	0.5	29	8	1	142	0.01	1	0.01	3.2	5	0.01
KL28-04	799.8	801.6	0.72	7200	0.19	1.5	71	7	0.01	12	0.01	15	0.01	9.8	18	0.01
KL28-04	801.6	804	0.445	4450	0.14	1	51	5	0.01	13	0.01	10	0.01	7.3	18	0.01
KL28-04	804	807	0.9	9000	0.3	2.6	110	7	3	35	0.01	18	0.01	13.1	22	0.01
KL28-04	807	810	0.476	4760	0.22	1.6	171	9	7	10	0.01	30	0.01	7.5	39	0.01
KL28-04	810	813	0.69	6900	0.23	2	102	7	4	31	0.01	21	0.01	7.8	26	0.01
KL28-04	813	816	0.95	9500	0.24	2.5	132	16	2	132	0.01	21	0.01	17.0	41	0.01
KL28-04	816	819	0.65	6500	0.17	1.6	71	8	12	25	0.01	16	0.01	13.3	31	0.01
KL28-04	819	822	1.43	14300	0.31	4	112	10	7	54	0.01	14	0.4	13.5	39	0.01
KL28-04	822	825	0.317	3170	0.08	0.8	28	8	16	14	0.01	8	0.01	10.8	29	0.01
KL28-04	825	828	1.37	13700	0.29	3.6	67	11	15	41	0.01	21	0.4	17.5	41	0.01
KL28-04	828	831	1.55	15500	0.37	4.1	98	14	7	90	0.01	13	0.01	14.5	46	0.01
KL28-04	831	834	0.75	7500	0.21	2	51	10	5	71	0.01	17	0.01	13.8	45	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL28-04	834	836	0.453		4530	0.13	1.8	67	10	2	26	0.01	13	0.01	13.3	50	0.01
KL28-04	836	839.1	0.194		1940	0.05	0.1	85	11	3	58	0.01	14	0.4	6.0	24	0.01
KL28-04	839.1	842.2	0.52		5200	0.15	1.2	88	70	2	37	0.01	16	0.01	9.4	22	0.01
KL28-04	842.2	845.3	1.18		11800	1.88	2.7	142	22	2	4	1	11	0.01	4.5	8	0.01
KL28-04	845.3	848.4	0.335		3350	0.12	0.8	89	9	10	16	0.01	15	2.2	11.9	14	0.01
KL28-04	848.4	851.5	1.11		11100	0.32	2.4	112	10	4	21	0.01	18	0.01	7.3	21	0.01
KL28-04	851.5	853.8	0.78		7800	0.17	1.8	75	15	4	21	0.01	14	0.2	6.3	20	0.01
KL28-04	853.8	855	0.3		3000	0.05	0.9	32	11	1	670	0.01	6	0.01	3.0	13	0.01
KL28-05	0	3	0.0123		123	0.01	0.1	63	23	6	1	0.01	1	0.3	0.5	21	0.01
KL28-05	3	6	0.0094		94	0.02	0.1	358	137	12	4	0.01	1	1	1.2	28	0.01
KL28-05	6	9	0.0083		83	0.03	0.1	520	88	13	1	0.01	1	1	0.5	28	0.01
KL28-05	9	12	0.0081		81	0.05	0.1	63	42	10	4	0.01	1	0.6	1.0	36	0.01
KL28-05	12	15	0.0154		154	0.01	0.1	44	43	8	14	0.01	1	0.5	1.0	35	0.01
KL28-05	15	18	0.0196		196	0.01	0.1	38	55	4	23	0.01	1	0.3	0.5	29	0.01
KL28-05	18	21	0.0037		37	0.01	0.1	40	41	6	1	0.01	1	0.01	1.0	27	0.01
KL28-05	21	24	0.0122		122	0.02	0.1	101	47	10	5	0.01	1	0.9	3.3	37	0.01
KL28-05	24	27	0.0035		35	0.02	0.1	62	40	12	2	0.01	1	0.4	1.0	44	0.01
KL28-05	27	30	0.0055		55	0.01	0.1	49	31	5	3	0.01	1	0.2	0.7	49	0.01
KL28-05	30	33	0.0034		34	0.01	0.1	38	19	6	3	0.01	1	0.3	0.7	53	0.01
KL28-05	33	36	0.004		40	0.01	0.1	50	38	4	1	0.01	1	0.4	1.0	33	0.01
KL28-05	36	39	0.0032		32	0.01	0.1	56	31	3	1	0.01	1	0.2	1.0	32	0.01
KL28-05	39	41	0.0043		43	0.01	0.8	328	343	14	7	1	1	1.2	2.4	22	0.01
KL28-05	41	43	0.0036		36	0.01	0.1	95	90	6	1	0.01	1	1.1	4.6	34	0.01
KL28-05	43	45	0.0034		34	0.02	1.8	170	147	8	4	2	1	2.1	0.0	39	0.01
KL28-05	45	48	0.0065		65	0.01	4.4	2270	3000	10	1	1	1	3.9	0.0	23	0.01
KL28-05	48	51	0.0034		34	0.06	1	258	363	20	2	2	7	1.7	0.0	134	0.01
KL28-05	51	52.8	0.48		4800	0.3	51	2740	5000	410	23	116	1	18.9	43.5	101	0.01
KL28-05	52.8	54.2	1.57		15700	0.48	101	5900	8600	410	26	344	7	10.2	46.7	186	0.43
KL28-05	54.2	57	0.0096		96	0.06	2.1	308	730	14	9	4	1	2.5	4.5	26	0.01
KL28-05	57	60	0.0134		134	0.03	1.5	94	97	37	4	16	1	3.1	4.1	49	0.01
KL28-05	60	63	0.0068		68	0.02	1.1	99	115	28	14	3	1	5.5	6.5	31	0.01
KL28-05	63	65.3	0.0124		124	0.02	0.1	105	137	7	23	0.01	1	2	0.8	43	0.01
KL28-05	65.3	67.2	0.0083		83	0.01	1.2	118	730	13	8	2	1	2.7	0.0	32	0.01
KL28-05	67.2	70.2	0.0138		138	0.1	2.3	258	2100	22	8	3	1	5.1	3.5	36	0.01
KL28-05	70.2	73.3	0.0152		152	0.15	1.1	147	410	18	11	0.01	1	3.5	1.1	36	0.01
KL28-05	73.3	76.3	0.0015		15	0.03	0.1	121	330	14	4	0.01	1	4.1	3.5	106	0.01
KL28-05	76.3	78	0.0095		95	0.12	0.7	133	720	19	5	1	1	7.4	1.7	36	0.01
KL28-05	78	81	0.0097		97	0.03	0.9	160	790	18	9	0.01	1	6.1	0.0	25	0.01
KL28-05	81	84	0.0026		26	0.01	1	246	680	10	14	0.01	1	2.6	1.4	10	0.01
KL28-05	84	87	0.0303		303	0.1	47	12600	3100	57	13	0.01	1	48	3.5	16	0.27
KL28-05	87	90	0.0023		23	0.01	2.3	440	370	41	4	0.01	1	5	0.0	56	0.01
KL28-05	90	93	0.0019		19	0.01	1.7	193	1040	31	5	0.01	1	4.5	0.0	18	0.01
KL28-05	93	96	0.0026		26	0.04	1.7	730	920	16	6	0.01	1	3.8	1.0	96	0.01
KL28-05	96	99	0.0021		21	0.02	3.3	380	250	3	6	2	1	1.9	1.7	28	0.01
KL28-05	99	101.8	0.0043		43	0.01	7.6	2250	2200	3	5	1	1	6	3.2	16	0.01
KL28-05	101.8	104.5	0.0037		37	0.04	5.1	900	1250	5	6	1	1	3.6	2.0	19	0.01
KL28-05	104.5	106.5	0.0028		28	0.02	2.8	560	900	2	2	0.01	1	2.2	1.2	15	0.01
KL28-05	106.5	109.5	0.003		30	0.01	2.2	400	1040	2	3	1	1	2.3	2.2	17	0.01
KL28-05	109.5	112	0.0029		29	0.01	2.1	530	1050	6	1	1	1	1.5	2.2	14	0.01
KL28-05	112	114.2	0.0035		35	0.01	2.7	610	1600	4	2	2	1	3.5	3.0	18	0.01
KL28-05	114.2	117	0.0035		35	0.01	1.5	172	870	2	5	0.01	1	4.2	1.7	21	0.01
KL28-05	117	119.9	0.0021		21	0.33	1	73	62	31	1	2	3	5.8	11.2	107	0.01
KL28-05	119.9	122.4	0.0029		29	0.01	1.8	392	1060	4	3	1	1	3	2.0	21	0.01
KL28-05	122.4	125.5	0.0061		61	0.01	4.1	400	760	7	4	3	1	1.8	0.0	15	0.01
KL28-05	125.5	128.3	0.0057		57	0.01	8.5	215	1050	10	3	8	1	1.6	2.0	24	0.01
KL28-05	128.3	130	0.118		1180	0.11	5.2	165	720	6	8	9	1	1.2	3.5	34	0.01
KL28-05	130	132.2	0.0066		66	0.01	2.6	230	520	7	1	2	1	0.8	1.7	22	0.01
KL28-05	132.2	135	0.0031		31	0.01	2.4	132	300	4	4	2	1	1.2	0.8	24	0.01
KL28-05	135	136.5	0.0013		13	0.01	3.2	65	570	2	1	3	1	1	0.0	23	0.01
KL28-05	136.5	138.5	0.0014		14	0.01	2	84	291	2	2	0.01	1	1.4	1.2	28	0.01
KL28-05	138.5	141	0.0017		17	0.03	5.8	76	580	7	12	0.01	1	2.7	2.2	30	0.01
KL28-05	141	144	0.0041		41	0.04	3.9	160	1010	6	7	0.01	1	2.8	1.2	34	0.01
KL28-05	144	147	0.004		40	0.01	1.9	260	348	2	3	0.01	1	1.1	0.7	25	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL28-05	147	150	0.0026		26	0.01	3.2	137	890	3	2	0.01	1	2	1.5	30	0.01
KL28-05	150	153	0.0015		15	0.01	1.5	155	323	4	10	0.01	1	1.2	1.0	15	0.01
KL28-05	153	156	0.0169		169	0.01	2.8	280	313	5	10	0.01	1	0.9	1.0	14	0.01
KL28-05	156	158.8	0.0038		38	0.02	19.7	1650	4900	7	11	0.01	1	12	1.5	12	0.01
KL28-05	158.8	161.3	0.0162		162	0.01	1.2	338	520	5	7	0.01	1	1.1	0.7	12	0.01
KL28-05	161.3	163.5	0.0031		31	0.01	2.1	650	730	6	14	3	1	1.3	1.7	13	0.01
KL28-05	163.5	166.5	0.001		10	0.01	2	480	680	4	7	0.01	1	0.9	0.7	12	0.01
KL28-05	166.5	169.5	0.003		30	0.01	2.5	2310	2400	5	12	0.01	1	2.2	1.7	14	0.01
KL28-05	169.5	172.3	0.0102		102	0.01	2.8	810	1030	3	11	0.01	1	1.6	1.2	15	0.01
KL28-05	172.3	174.3	0.0013		13	0.01	0.9	64	205	5	1	0.01	1	0.7	0.0	13	0.01
KL28-05	174.3	177	0.001		10	0.01	0.6	124	147	10	8	0.01	1	0.5	0.7	16	0.01
KL28-05	177	180	0.0042		42	0.01	1.9	1050	1820	12	11	0.01	1	1.2	2.7	16	0.01
KL28-05	180	183	0.0316		316	0.23	28.1	8600	20200	22	168	1	1	19.5	13.0	17	0.01
KL28-05	183	184.5	0.0257		257	0.23	19.2	2700	15700	66	365	2	1	17.6	10.6	25	0.01
KL28-05	184.5	187.5	0.0105		105	0.07	3.2	1300	3000	18	95	0.01	1	3.4	3.5	16	0.01
KL28-05	187.5	190.5	0.006		60	0.07	1.9	1980	2400	8	56	0.01	1	2.8	2.7	17	0.01
KL28-05	190.5	192	0.0039		39	0.07	1.8	2000	2400	11	22	0.01	1	1.6	2.0	30	0.01
KL28-05	192	195	0.0038		38	0.05	1.6	980	1260	12	18	0.01	1	1.7	2.7	21	0.01
KL28-05	195	197.5	0.0075		75	0.02	1.7	1120	1280	7	15	0.01	1	1.9	2.8	13	0.01
KL28-05	197.5	200.6	0.0016		16	0.01	0.9	570	700	8	11	0.01	1	1.1	1.2	12	0.01
KL28-05	200.6	203.2	0.013		130	0.02	0.6	340	286	5	7	0.01	1	0.8	1.2	12	0.01
KL28-05	203.2	205.5	0.0032		32	0.01	1.9	1260	1230	5	7	0.01	1	1.4	3.5	9	0.01
KL28-05	205.5	208.5	0.0186		186	0.16	7.8	1250	4800	28	186	23	2	4.3	42.5	18	0.01
KL28-05	208.5	211.5	0.0033		33	0.07	1.8	540	1060	19	26	0.01	1	1.8	7.1	16	0.01
KL28-05	211.5	214.8	0.0091		91	0.15	8.3	9400	4900	15	15	4	1	9	9.3	10	0.39
KL28-05	214.8	217.2	0.0229		229	0.14	29.1	10100	13800	54	19	42	1	18.7	9.2	11	0.44
KL28-05	217.2	220.2	0.0024		24	0.04	0.9	317	580	8	6	0.01	1	1.1	1.0	19	0.01
KL28-05	220.2	222.2	0.0013		13	0.02	0.7	292	580	7	7	0.01	1	0.7	1.1	14	0.01
KL28-05	222.2	223.5	0.0063		63	0.03	5.6	5000	6500	7	52	5	2	6.3	4.5	12	0.01
KL28-05	223.5	226.5	0.0028		28	0.01	1.6	1260	1520	14	11	0.01	1	1.8	5.0	16	0.01
KL28-05	226.5	228	0.0067		67	0.03	4.7	5800	3700	28	18	2	2	4.5	4.7	10	0.01
KL28-05	228	231	0.0195		195	0.05	10.8	9400	7000	42	30	7	2	7.7	10.0	23	0.01
KL28-05	231	234	0.0111		111	0.06	7.5	3200	4100	35	17	8	1	3.7	7.0	11	0.01
KL28-05	234	236	0.0194		194	0.12	3.8	2350	1350	52	34	11	1	2.7	6.3	13	0.01
KL28-05	236	238.5	0.0391		391	0.23	37	20900	31800	34	29	135	18	2.9	211.0	25	0.01
KL28-05	238.5	241.5	0.0273		273	0.1	1.7	1060	1000	32	112	4	3	0.6	6.3	29	0.01
KL28-05	241.5	244.5	0.0106		106	0.04	0.9	278	212	17	1920	4	1	0.7	5.5	187	0.01
KL28-05	244.5	246.5	0.0086		86	0.02	1	153	220	12	1050	3	1	0.3	3.2	85	0.01
KL28-05	246.5	249	0.0141		141	0.03	0.6	187	110	9	900	4	1	0.3	3.0	74	0.01
KL28-05	249	252	0.0114		114	0.14	0.1	264	164	12	468	4	1	0.7	2.5	164	0.01
KL28-05	252	255	0.27		2700	1	3.8	23500	700	68	258	90	15	2.2	18.8	21	0.17
KL28-05	255	258	0.38		3800	1.27	24.6	68500	2730	57	1270	580	38	1.5	40.0	55	0.01
KL28-05	258	261	0.121		1210	5.99	6.7	4600	760	230	1580	120	4	8.6	16.3	160	1.08
KL28-05	261	264	0.163		1630	6.71	12.8	25300	2090	180	212	280	15	7.7	28.5	57	0.66
KL28-05	264	267	0.66		6600	1.52	17.8	9100	550	54	198	293	14	2	25.5	61	0.2
KL28-05	267	270	0.197		1970	0.67	2.7	49600	335	34	70	8	55	0.4	38.8	57	0.01
KL28-05	270	273	0.4		4000	2.17	6.8	15300	60	130	18	98	14	1.3	43.5	39	0.11
KL28-05	273	276	1.19		11900	3.56	15.3	7600	1970	360	470	6	74	16.8	24.0	174	1.2
KL28-05	276	279	0.67		6700	2.1	23.8	2550	2800	490	930	6	28	80	17.5	152	1.4
KL28-05	279	280.9	0.117		1170	1.3	9.8	1780	1310	170	740	8	29	37	25.5	124	0.17
KL28-05	280.9	283.4	0.99		9900	1.12	17.4	10900	1370	32	265	69	88	9	19.3	80	0.01
KL28-05	283.4	285	1.35		13500	1.06	21.6	13900	1500	22	101	90	105	1.6	21.7	69	0.01
KL28-05	285	288	0.92		9200	0.9	14.2	12100	1520	30	164	68	61	1.2	15.3	60	0.01
KL28-05	288	291	0.5		5000	1.76	11.3	25000	3500	260	102	52	104	12.8	17.5	200	0.24
KL28-05	291	294	1.67		16700	2.46	21.7	24400	6610	260	82	77	86	6.4	32.3	198	0.64
KL28-05	294	297	2.7		27000	1.72	13.7	1250	249	27	152	9	195	1.8	27.0	217	0.01
KL28-05	297	300	2.29		22900	1.34	8.7	2600	630	28	101	8	70	1.3	17.0	126	0.01
KL28-05	300	303	2.24		22400	0.88	7.7	520	89	17	485	12	68	1.1	15.5	219	0.01
KL28-05	303	306	1.52		15200	0.56	5.9	372	111	15	259	16	48	1.3	9.3	158	0.01
KL28-05	306	309	1.96		19600	0.96	5.1	610	112	11	95	8	65	0.6	14.5	57	0.01
KL28-05	309	312	1.87		18700	1.08	5.8	289	54	3	630	14	46	0.2	14.5	90	0.01
KL28-05	312	315	1.79		17900	1.92	17	9400	16000	800	189	4	37	38	11.8	81	1.16
KL28-05	315	318	3.04		30400	2.5	5.7	3100	830	14	166	3	87	1.8	19.0	91	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL28-05	318	319.6	5.36	53600	3.34	4.3	750	67	4	880	1	87	0.6	8.3	72	0.01
KL28-05	319.6	321.8	7.13	71300	3.18	6.4	330	43	2	237	0.01	100	0.4	7.5	94	0.01
KL28-05	321.8	323.6	1.86	18600	1.13	4	1050	990	160	1800	1	20	2.8	17.0	188	0.32
KL28-05	323.6	325.1	2.15	21500	0.96	2.5	670	133	110	890	1	30	1.1	11.0	148	0.22
KL28-05	325.1	327	2.58	25800	1.48	2.2	82	26	1	150	0.01	26	0.01	12.5	139	0.01
KL28-05	327	330	1.67	16700	0.87	1.7	209	52	3	670	0.01	24	0.6	10.5	192	0.01
KL28-05	330	333	1.3	13000	0.81	1.8	80	41	0.01	510	0.01	11	0.01	9.0	98	0.01
KL28-05	333	336	1.43	14300	1.03	1.4	118	36	0.01	223	0.01	10	0.01	8.8	100	0.01
KL28-05	336	339	1.54	15400	0.97	1.4	52	22	1	351	0.01	11	0.01	6.3	106	0.01
KL28-05	339	342	1.54	15400	0.92	2.8	133	64	71	336	1	12	14	10.8	215	0.1
KL28-05	342	345	2.24	22400	1.61	3.8	109	30	10	234	2	6	0.2	9.6	169	0.01
KL28-05	345	348	1.52	15200	1.92	2.3	39	17	8	108	0.01	8	0.01	10.0	116	0.01
KL28-05	348	350.5	1.69	16900	1.05	2.2	50	20	3	100	0.01	13	0.4	6.5	148	0.01
KL28-05	350.5	353.5	1.26	12600	1.69	1.8	30	13	16	82	0.01	8	1.7	8.8	154	0.01
KL28-05	353.5	356.6	1.75	17500	1.57	2.7	65	25	29	50	1	11	0.01	9.9	114	0.01
KL28-05	356.6	359.6	1.79	17900	1.52	3.6	28	9	0.01	50	1	12	0.01	11.0	123	0.01
KL28-05	359.6	362.7	1.16	11600	0.84	2.3	30	9	1	98	0.01	10	0.01	7.9	181	0.01
KL28-05	362.7	365.8	1.06	10600	0.67	2.2	37	15	1	84	1	10	0.2	3.8	106	0.01
KL28-05	365.8	368.9	1.5	15000	1.32	3.6	36	14	2	59	2	12	0.2	10.1	70	0.01
KL28-05	368.9	372	0.89	8900	0.78	3.2	410	200	120	104	2	11	5.1	7.5	66	0.01
KL28-05	372	375	0.71	7100	0.69	2.1	223	37	8	96	2	11	0.6	5.8	69	0.01
KL28-05	375	378	0.86	8600	0.72	1.9	133	23	5	48	1	16	0.2	6.8	78	0.01
KL28-05	378	381	1.48	14800	1.85	3.4	71	14	4	37	3	13	0.3	10.0	79	0.01
KL28-05	381	384	1.28	12800	1.93	2.1	32	8	1	24	2	9	0.01	11.3	76	0.01
KL28-05	384	387	0.85	8500	0.63	2.3	42	9	0.01	66	3	13	0.01	5.3	82	0.01
KL28-05	387	390	0.81	8100	0.68	1.7	33	8	1	36	1	11	0.01	5.8	73	0.01
KL28-05	390	393	0.98	9800	0.67	2.3	47	8	1	38	2	12	0.01	5.3	78	0.01
KL28-05	393	395.3	1.02	10200	0.82	2.6	40	8	1	36	2	9	0.01	6.8	91	0.01
KL28-05	395.3	398.3	1.63	16300	1.32	3.5	38	12	1	29	4	8	0.01	14.0	112	0.01
KL28-05	398.3	401.4	1.88	18800	1.92	3.7	102	70	1	30	9	6	0.01	11.5	123	0.01
KL28-05	401.4	404.5	2.14	21400	2.25	5.8	45	26	1	81	15	10	1.2	14.0	106	0.01
KL28-05	404.5	407.6	3.35	33500	2.45	6.5	91	55	6	184	6	15	0.2	7.0	80	0.01
KL28-05	407.6	409.2	1.16	11600	0.34	1.7	38	17	6	156	4	3	0.3	9.0	90	0.01
KL28-05	409.2	411	0.87	8700	0.64	1.7	17	6	3	309	1	3	0.01	7.0	124	0.01
KL28-05	411	414	0.85	8500	0.62	1.8	47	12	2	71	0.01	6	0.01	7.5	118	0.01
KL28-05	414	417	0.72	7200	0.31	2.2	440	470	31	46	1	3	17	5.5	126	0.01
KL28-05	417	420	0.89	8900	0.25	1.4	143	57	22	90	2	4	5.9	9.1	129	0.01
KL28-05	420	423	1.28	12800	0.92	2.4	32	15	1	28	1	12	0.01	9.8	146	0.01
KL28-05	423	426	1.5	15000	0.52	2.1	53	24	10	29	3	3	0.3	8.6	205	0.01
KL28-05	426	429	1.23	12300	0.81	3	154	103	26	36	2	10	6.2	8.5	134	0.01
KL28-05	429	432	0.76	7600	0.08	1.1	36	23	48	33	2	2	0.7	6.4	121	0.01
KL28-05	432	435	0.53	5300	0.08	0.8	20	12	6	24	1	1	0.01	8.3	142	0.01
KL28-05	435	438	1.08	10800	0.77	1.8	17	8	0.01	52	2	6	0.01	8.5	141	0.01
KL28-05	438	441	1.16	11600	0.8	2.2	76	16	4	38	1	7	0.8	7.1	172	0.01
KL28-05	441	444	1.03	10300	0.61	1.6	22	19	1	168	1	9	0.01	6.3	174	0.01
KL28-05	444	447	1.02	10200	0.47	1.7	87	40	57	64	1	10	0.9	6.5	172	0.01
KL28-05	447	450	1.15	11500	0.48	2.6	245	81	71	46	1	11	2.4	8.3	154	0.01
KL28-05	450	453	0.95	9500	0.57	2	175	38	280	61	1	12	0.7	7.0	120	0.01
KL28-05	453	456	1.18	11800	0.86	2.1	99	33	17	26	5	4	16.9	8.5	147	0.01
KL28-05	456	459	0.71	7100	0.72	1.2	38	19	5	24	4	4	0.2	5.0	118	0.01
KL28-05	459	462	0.41	4100	0.16	0.8	54	16	17	69	1	2	0.6	4.3	136	0.01
KL28-05	462	465	0.9	9000	0.46	1	21	11	2	54	2	3	0.01	5.5	140	0.01
KL28-05	465	468	1.36	13600	1.5	2.1	25	10	7	37	2	6	8.2	8.1	196	0.01
KL28-05	468	470	1.06	10600	0.65	1.2	21	6	1	18	1	7	0.4	7.0	160	0.01
KL28-05	470	471.9	0.68	6800	0.45	0.6	26	9	6	66	0.01	4	1.3	5.0	191	0.01
KL28-05	471.9	474	0.38	3800	0.12	0.1	58	24	13	168	1	2	0.6	5.4	191	0.01
KL28-05	474	477	1	10000	0.34	1.4	122	44	11	48	1	6	0.9	6.3	178	0.01
KL28-05	477	480	1.18	11800	0.67	1.6	24	8	2	50	1	11	0.01	6.8	214	0.01
KL28-05	480	483	0.99	9900	0.53	2.3	83	10	1	36	1	11	0.01	4.8	146	0.01
KL28-05	483	486	0.76	7600	0.47	2	75	10	1	38	0.01	13	0.01	6.0	156	0.01
KL28-05	486	488	0.98	9800	0.51	2.3	66	6	0.01	48	0.01	15	0.01	6.2	193	0.01
KL28-05	488	491.1	1.3	13000	0.91	2	260	20	7	46	0.01	12	0.2	8.6	158	0.01
KL28-05	491.1	494.2	1.16	11600	0.57	2.9	108	119	180	25	0.01	15	16	9.3	96	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL28-05	494.2	497.3	1.54	15400	0.81	2.6	211	48	31	31	0.01	11	0.8	8.2	109	0.01
KL28-05	497.3	500.4	1.19	11900	0.88	1.5	22	7	3	33	0.01	10	0.01	6.8	138	0.01
KL28-05	500.4	503.5	0.83	8300	0.67	1.3	120	38	33	48	0.01	8	0.4	6.7	115	0.01
KL28-05	503.5	506.6	1.09	10900	0.76	2.4	148	66	13	40	0.01	11	0.2	7.0	123	0.01
KL28-05	506.6	509.8	0.58	5800	0.32	14.1	1080	1400	260	33	0.01	11	154	8.0	95	0.1
KL28-05	509.8	512.8	0.54	5400	0.43	1.5	35	9	2	67	0.01	10	0.01	4.0	102	0.01
KL28-05	512.8	515.8	0.45	4500	0.17	1.8	550	369	11	40	0.01	8	4.5	5.3	110	0.01
KL28-05	515.8	518.9	0.402	4020	0.21	1.2	30	17	2	78	0.01	7	0.01	4.1	136	0.01
KL28-05	518.9	522	0.529	5290	0.25	2.8	860	320	37	86	0.01	8	12	4.5	130	0.01
KL28-05	522	525	0.67	6700	0.37	2	77	20	7	74	0.01	8	0.3	5.0	131	0.01
KL28-05	525	528	0.502	5020	0.25	1.4	36	15	2	85	0.01	7	0.3	5.5	147	0.01
KL28-05	528	531	0.443	4430	0.19	1.4	33	11	1	93	0.01	6	0.01	4.8	130	0.01
KL28-05	531	534	0.8	8000	0.34	14.7	4200	9800	570	193	2	5	86	12.4	181	0.41
KL28-05	534	537	0.379	3790	0.15	1.6	720	287	15	148	1	9	1.9	4.5	127	0.01
KL28-05	537	540	0.7	7000	0.34	2.3	167	100	4	72	0.01	8	0.3	6.5	135	0.01
KL28-05	540	543	0.68	6800	0.27	3.1	283	406	28	50	0.01	12	6.3	7.3	131	0.01
KL28-05	543	546	0.439	4390	0.2	1.3	47	32	4	83	0.01	6	0.7	4.2	173	0.01
KL28-05	546	549	0.506	5060	0.27	1.5	20	13	2	47	0.01	7	0.01	6.3	153	0.01
KL28-05	549	552	1.06	10600	0.56	2.5	71	32	22	60	1	15	0.3	9.3	170	0.01
KL28-05	552	555	0.72	7200	0.34	3	90	56	17	62	0.01	13	0.6	8.3	123	0.01
KL28-05	555	558	0.417	4170	0.2	1.5	133	65	18	44	0.01	7	2.2	6.3	106	0.01
KL28-05	558	561	0.46	4600	0.19	2.2	152	82	15	68	0.01	8	1.6	7.8	101	0.01
KL28-05	561	564	0.428	4280	0.22	1.4	45	26	3	98	0.01	8	0.7	6.3	123	0.01
KL28-05	564	567	0.55	5500	0.2	5.1	1350	480	190	178	1	7	54	8.5	106	0.14
KL28-05	567	570	0.74	7400	0.4	3	294	254	10	46	0.01	12	1.2	9.0	132	0.01
KL28-05	570	573	0.532	5320	0.23	1.7	48	14	3	70	0.01	11	0.4	7.4	209	0.01
KL28-05	573	576	0.508	5080	0.2	2.1	49	20	0.01	93	0.01	8	0.01	6.8	90	0.01
KL28-05	576	579	0.449	4490	0.19	1.4	41	10	1	159	0.01	7	0.2	5.9	215	0.01
KL28-05	579	582	0.64	6400	0.29	1.8	53	12	1	197	0.01	10	0.01	7.8	108	0.01
KL28-05	582	585	0.55	5500	0.2	1.9	85	50	1	149	0.01	14	0.8	6.3	180	0.01
KL28-05	585	588	0.59	5900	0.13	1.7	88	27	5	86	0.01	9	0.6	5.8	84	0.01
KL28-05	588	591	0.455	4550	0.14	1.6	124	67	3	45	0.01	6	0.2	5.5	94	0.01
KL28-05	591	594	0.7	7000	0.19	4.1	162	121	46	112	3	10	7.6	7.8	185	0.01
KL28-05	594	597	0.495	4950	0.11	6.3	76	82	81	97	7	9	11.4	7.5	200	0.01
KL28-05	597	600	0.481	4810	0.1	1.8	92	86	8	88	1	5	2.4	4.8	225	0.01
KL28-05	600	602.5	0.54	5400	0.1	2.6	198	69	25	39	0.01	6	5.3	6.3	163	0.01
KL28-05	602.5	604.5	1.08	10800	0.23	9.3	3600	1670	250	85	0.01	10	102	6.3	145	0.39
KL28-05	604.5	606.7	2.9	29000	1.33	8.9	3500	650	11	108	1	110	4.1	11.0	88	0.12
KL28-05	606.7	609	0.69	6900	0.25	1.1	112	20	1	19	1	112	0.3	14.6	42	0.01
KL28-05	609	612	0.57	5700	0.39	1.2	108	27	1	10	1	37	0.7	11.8	41	0.01
KL28-05	612	615	1.16	11600	0.72	2.5	233	25	1	6	1	50	0.3	9.0	46	0.01
KL28-05	615	617.3	1.1	11000	0.76	2.7	137	10	2	30	0.01	45	0.5	10.3	46	0.01
KL28-05	617.3	619.2	0.66	6600	0.4	1.8	139	26	2	62	0.01	24	0.3	11.3	34	0.01
KL28-05	619.2	621.3	0.69	6900	0.52	1.6	85	8	2	68	0.01	14	0.01	11.5	35	0.01
KL28-05	621.3	624	1.3	13000	1.1	3.1	94	10	0.01	8	0.01	12	0.01	7.0	28	0.01
KL28-05	624	627	0.72	7200	0.93	2.2	105	12	8	238	0.01	13	16.2	6.3	30	0.01
KL28-05	627	630	0.491	4910	0.63	1.5	97	11	20	333	0.01	16	8.7	6.8	48	0.01
KL28-05	630	633	0.72	7200	0.63	2.1	138	10	8	20	0.01	18	1	11.0	70	0.01
KL28-05	633	636	1.05	10500	0.6	2.7	127	12	3	20	0.01	19	0.4	20.0	66	0.01
KL28-05	636	639	1.46	14600	0.64	4	152	10	3	163	0.01	25	0.6	15.7	65	0.01
KL28-05	639	642	0.74	7400	0.48	2.9	129	24	1	41	0.01	26	0.2	14.8	44	0.01
KL28-05	642	645	0.8	8000	0.44	2	119	18	7	28	0.01	35	1	23.6	48	0.01
KL28-05	645	648	0.149	1490	0.04	0.8	57	27	3	35	0.01	10	0.5	4.5	32	0.01
KL28-05	648	651	0.9	9000	0.12	2	127	32	1	9	0.01	12	0.01	3.0	90	0.01
KL28-05	651	654	0.281	2810	0.1	1	79	25	3	20	0.01	15	0.2	6.3	45	0.01
KL28-05	654	657	0.267	2670	0.1	1.2	76	23	3	21	0.01	14	0.2	6.3	44	0.01
KL28-05	657	660	0.427	4270	0.09	1.5	67	25	3	120	0.01	10	0.01	8.0	28	0.01
KL28-05	660	663	0.367	3670	0.11	1.4	50	22	1	30	0.01	7	0.01	7.0	31	0.01
KL28-05	663	666	0.288	2880	0.12	1	43	16	1	35	0.01	7	0.01	6.3	27	0.01
KL28-05	666	668	0.6	6000	0.25	1.5	74	15	1	118	0.01	21	0.2	9.0	45	0.01
KL28-05	668	671	0.357	3570	0.27	1.1	78	25	4	14	0.01	15	0.3	6.5	47	0.01
KL28-05	671	674	0.476	4760	0.2	1.4	73	28	0.01	21	0.01	10	0.01	7.3	43	0.01
KL28-05	674	677.2	0.61	6100	0.33	1.7	75	19	2	29	0.01	16	0.01	10.4	35	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL28-05	677.2	680.3	0.142	1420	0.1	0.7	35	9	0.01	238	0.01	6	0.01	4.0	45	0.01
KL28-05	680.3	683.4	0.242	2420	0.14	0.8	50	13	1	21	0.01	7	0.01	5.0	43	0.01
KL28-05	683.4	686.5	0.38	3800	0.35	1.1	62	23	0.01	11	0.01	7	0.01	6.5	51	0.01
KL28-05	686.5	689.6	0.421	4210	0.31	2.4	67	26	1	6	0.01	9	0.01	6.8	35	0.01
KL28-05	689.6	693	0.284	2840	0.09	1.3	41	18	1	10	0.01	6	0.2	7.0	25	0.01
KL28-05	693	696	0.204	2040	0.05	1.2	66	39	8	18	0.01	7	2.7	6.3	83	0.01
KL28-05	696	699.3	0.375	3750	0.1	1.4	56	26	0.01	21	0.01	8	0.4	8.5	78	0.01
KL28-05	699.3	701.4	0.139	1390	0.05	1	74	33	18	52	0.01	9	17.5	5.2	160	0.01
KL28-05	701.4	704.8	1.16	11600	0.46	3.3	146	14	1	81	0.01	65	0.5	10.6	35	0.01
KL28-05	704.8	707.9	0.128	1280	0.05	0.1	41	12	2	45	0.01	12	0.3	3.3	30	0.01
KL28-05	707.9	711	0.21	2100	0.05	0.9	39	20	1	80	0.01	6	0.6	4.3	41	0.01
KL28-05	711	714	0.115	1150	0.04	1.1	66	24	43	35	0.01	4	2.3	3.5	105	0.01
KL28-05	714	717	0.117	1170	0.02	2.4	325	152	110	48	0.01	2	20	2.3	163	0.01
KL28-05	717	720	0.104	1040	0.04	1.1	212	178	13	38	0.01	5	2.3	2.8	90	0.01
KL28-05	720	723	0.14	1400	0.13	1.2	590	435	24	47	0.01	7	2	7.0	50	0.01
KL28-05	723	726	0.059	590	0.03	0.1	31	12	1	660	0.01	2	0.5	3.0	23	0.01
KL28-05	726	729	0.137	1370	0.05	0.8	76	13	2	69	0.01	9	0.6	3.4	17	0.01
KL28-05	729	732	0.061	610	0.03	1.9	40	21	1	16	0.01	3	0.7	2.5	12	0.01
KL28-05	732	735	0.131	1310	0.06	0.1	25	12	0.01	19	1	5	0.4	5.5	16	0.01
KL28-05	735	738	0.4	4000	0.16	1.7	83	20	15	78	0.01	20	0.6	8.8	31	0.01
KL28-05	738	740.2	0.099	990	0.04	0.1	82	13	0.01	18	0.01	28	0.01	8.5	26	0.01
KL28-05	740.2	743	0.498	4980	0.15	1.5	128	6	1	17	0.01	34	0.01	7.0	37	0.01
KL28-05	743	746	0.256	2560	0.09	0.7	93	12	0.01	24	0.01	28	0.01	6.3	30	0.01
KL28-05	746	748	0.174	1740	0.07	0.1	84	9	0.01	20	0.01	37	0.01	6.0	37	0.01
KL28-05	748	750	0.112	1120	0.05	0.8	76	6	0.01	9	0.01	27	0.2	3.0	31	0.01
KL28-05	750	753	0.29	2900	0.07	0.1	67	14	0.01	13	0.01	45	0.01	15.4	45	0.01
KL28-05	753	756	0.101	1010	0.06	0.9	167	36	0.01	21	0.01	25	0.01	5.5	37	0.01
KL28-05	756	759	0.35	3500	0.08	1	78	11	0.01	26	0.01	40	0.01	10.5	16	0.01
KL28-05	759	762.9	0.47	4700	0.1	1.3	97	17	0.01	8	0.01	28	0.01	6.3	21	0.01
KL28-05	762.9	765	0.98	9800	0.43	2.4	144	9	0.01	18	0.01	56	0.01	25.5	22	0.01
KL28-05	765	768	0.9	9000	0.43	2.8	120	13	0.01	13	0.01	42	0.01	11.8	28	0.01
KL28-05	768	770.7	0.359	3590	0.11	1.3	97	11	1	14	0.01	41	0.01	12.4	31	0.01
KL28-05	770.7	774	0.354	3540	0.13	1.1	110	18	2	163	0.01	42	0.01	8.8	31	0.01
KL28-05	774	777	0.173	1730	0.11	0.1	90	15	4	7	0.01	19	0.2	3.3	27	0.01
KL28-05	777	780	0.329	3290	0.13	0.8	86	33	3	175	0.01	14	0.4	6.0	30	0.01
KL28-05	780	783	0.148	1480	0.05	0.1	41	11	2	92	0.01	10	0.01	3.3	27	0.01
KL28-05	783	786	0.163	1630	0.09	5.3	5010	5040	55	73	2	9	12.2	5.0	22	0.54
KL28-05	786	789	0.073	730	0.03	0.1	38	13	2	18	0.01	2	0.5	1.8	23	0.01
KL28-05	789	792	0.08	800	0.02	0.1	38	17	1	67	0.01	3	0.3	2.3	18	0.01
KL28-05	792	795	0.344	3440	0.08	1	84	12	1	29	0.01	8	0.2	3.3	30	0.01
KL28-05	795	798	0.136	1360	0.04	0.9	44	13	0.01	72	0.01	5	0.2	2.1	23	0.01
KL28-05	798	801	0.301	3010	0.24	5.5	5400	5900	48	31	2	4	8.9	6.5	37	0.32
KL28-05	801	804	0.082	820	0.02	0.1	32	11	2	15	0.01	5	0.2	3.3	17	0.01
KL28-05	804	807	0.073	730	0.03	0.1	29	17	4	26	0.01	9	0.2	3.3	14	0.01
KL28-05	807	810	0.269	2690	0.1	0.1	50	7	2	11	0.01	16	0.01	5.5	17	0.01
KL28-05	810	813	0.072	720	0.03	0.1	27	6	0.01	30	0.01	8	0.01	2.8	16	0.01
KL28-05	813	816	0.137	1370	0.03	0.6	28	12	1	56	0.01	6	0.3	2.3	18	0.01
KL28-05	816	819	0.065	650	0.05	2.1	1360	820	45	15	0.01	3	7.9	3.8	19	0.01
KL28-05	819	822	0.36	3600	0.16	0.9	76	24	2	20	0.01	19	0.01	5.3	16	0.01
KL28-05	822	825	0.83	8300	0.27	1.3	141	26	3	136	0.01	23	0.01	7.1	17	0.01
KL28-05	825	828	0.485	4850	0.16	1	78	15	1	31	0.01	20	0.01	7.8	20	0.01
KL28-05	828	831	0.59	5900	0.33	0.8	70	6	0.01	12	0.01	20	0.01	7.8	35	0.01
KL28-05	831	833.3	0.58	5800	0.39	0.7	58	14	0.01	15	0.01	15	0.01	8.0	72	0.01
KL28-05	833.3	835.8	0.61	6100	0.3	0.8	48	27	0.01	30	0.01	8	0.01	5.3	70	0.01
KL28-05	835.8	838	0.0161	161	0.01	0.1	43	58	6	3	0.01	1	0.3	0.0	35	0.01
KL28-05	838	840	0.314	3140	0.04	0.1	17	6	2	103	0.01	1	0.2	3.8	94	0.01
KL28-05	840	843	0.074	740	0.01	0.1	37	8	9	40	0.01	1	0.01	1.5	186	0.01
KL28-06	0	3	0.0039	39	0.02	0.1	25	26	10	5	0.01	3	0.4	1.2	20	0.01
KL28-06	3	6	0.0071	71	0.01	0.1	54	20	12	5	0.01	4	0.4	1.2	22	0.01
KL28-06	6	9	0.0029	29	0.01	0.1	78	37	5	3	0.01	1	0.4	0.8	23	0.01
KL28-06	9	12	0.0027	27	0.04	0.1	165	78	7	3	0.01	1	1	1.2	26	0.01
KL28-06	12	15	0.0024	24	0.07	0.1	305	113	11	4	0.01	1	1	1.8	29	0.01
KL28-06	15	18	0.0034	34	0.02	0.1	128	242	11	4	1	1	1	1.2	23	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL28-06	18	21	0.0042		42	0.02	2.2	262	580	9	14	6	1	1.3	6.0	28	0.01
KL28-06	21	24	0.051		510	0.08	60	14100	22900	21	65	156	3	3.8	150.0	45	0.01
KL28-06	24	27	0.0064		64	0.09	48	890	4360	35	15	162	3	2.1	170.0	18	0.01
KL28-06	27	30	0.0029		29	0.01	2.1	400	1290	16	7	5	2	1.2	15.3	25	0.01
KL28-06	30	33	0.001		10	0.01	0.1	122	186	13	3	1	3	0.9	6.8	19	0.01
KL28-06	33	36	0.0017		17	0.03	0.1	193	124	16	5	1	1	1.3	2.3	25	0.01
KL28-06	36	39	0.0053		53	0.01	0.1	74	159	12	4	0.01	2	1.1	2.5	22	0.01
KL28-06	39	42	0.0026		26	0.01	0.1	75	116	7	3	0.01	2	0.6	1.8	28	0.01
KL28-06	42	45	0.0019		19	0.01	0.1	42	35	6	2	0.01	1	0.7	1.5	31	0.01
KL28-06	45	48	0.0016		16	0.01	0.1	54	31	1	3	0.01	2	0.4	1.3	39	0.01
KL28-06	48	51	0.0013		13	0.01	0.1	71	30	4	2	0.01	1	0.5	2.0	36	0.01
KL28-06	51	54	0.0012		12	0.01	0.1	38	28	3	2	0.01	1	0.3	1.5	23	0.01
KL28-06	54	57	0.0011		11	0.02	0.1	176	94	5	3	0.01	1	0.4	1.8	24	0.01
KL28-06	57	60	0.0062		62	0.72	3.8	970	2480	73	6	2	2	9	10.8	38	0.1
KL28-06	60	63	0.0178		178	0.35	2.7	460	340	65	4	3	3	5.6	11.8	224	0.01
KL28-06	63	66	0.0062		62	0.11	0.8	182	86	18	4	4	3	3.6	10.0	65	0.01
KL28-06	66	69	0.0096		96	0.27	1.8	386	244	25	3	8	4	7.6	10.0	133	0.01
KL28-06	69	72	0.0064		64	0.19	1.5	2010	850	19	5	3	5	2.4	8.8	85	0.01
KL28-06	72	75	0.82		8200	0.16	14.1	2800	1600	380	15	58	3	19.2	49.5	54	0.01
KL28-06	75	78	0.106		1060	0.2	122	1170	5200	110	24	1275	1	11	227.0	82	0.01
KL28-06	78	81	0.067		670	0.12	6.9	409	600	43	17	35	4	2.7	17.0	131	0.01
KL28-06	81	84	0.0362		362	0.11	4.2	184	740	19	14	12	1	3.5	4.8	47	0.01
KL28-06	84	87	0.0114		114	0.02	1.3	208	1210	12	12	2	1	1.9	1.2	52	0.01
KL28-06	87	90	0.0078		78	0.01	4.1	146	1760	10	10	8	1	2.2	1.8	62	0.01
KL28-06	90	93	0.0028		28	0.06	2	113	359	15	5	3	6	3.7	1.2	44	0.01
KL28-06	93	96	0.012		120	0.16	3.5	480	2100	46	10	7	1	5.8	5.0	176	0.01
KL28-06	96	99	0.0048		48	0.03	1.8	195	730	10	9	3	1	3	4.3	66	0.01
KL28-06	99	102	0.003		30	0.06	4	480	920	19	7	9	1	4	1.0	117	0.01
KL28-06	102	105	0.011		110	0.07	2.7	105	590	15	11	5	1	4.7	1.2	46	0.01
KL28-06	105	108	0.0189		189	0.12	2.9	168	510	21	8	5	1	6.9	1.8	60	0.01
KL28-06	108	111	0.015		150	0.02	4.5	800	1480	10	10	11	1	2.5	9.8	25	0.01
KL28-06	111	114	0.0104		104	0.05	2	70	400	11	17	5	1	2.2	2.3	57	0.01
KL28-06	114	117	0.0034		34	0.01	1.3	76	352	16	16	3	1	2.1	1.0	66	0.01
KL28-06	117	120	0.0024		24	0.01	0.8	226	215	24	5	0.01	1	2	2.5	17	0.01
KL28-06	120	123	0.0026		26	0.01	1.1	89	340	20	9	0.01	1	1.6	1.0	12	0.01
KL28-06	123	126	0.051		510	0.18	14.9	2900	15300	23	70	4	3	9.4	18.5	18	0.01
KL28-06	126	129.5	0.024		240	0.08	17.5	4900	13900	47	45	18	3	10	24.8	25	0.01
KL28-06	129.5	132	0.0074		74	0.02	6.9	1530	3450	10	10	5	2	3.8	4.8	20	0.01
KL28-06	132	135	0.0053		53	0.06	5.3	1080	2100	23	11	5	3	4.1	6.3	12	0.01
KL28-06	135	138	0.0066		66	0.02	3.7	1390	2100	9	26	1	3	3.6	4.0	18	0.01
KL28-06	138	140.8	0.0096		96	0.04	7.6	1640	5800	14	55	1	2	6.7	6.8	28	0.01
KL28-06	140.8	144.6	0.0039		39	0.01	8.6	970	3270	8	7	8	1	3.4	8.5	18	0.01
KL28-06	144.6	147.4	0.002		20	0.01	4.9	305	660	6	24	1	2	1.4	1.8	17	0.01
KL28-06	147.4	149.9	0.0317		317	0.09	28	8400	17200	23	19	5	1	14.4	10.5	23	0.01
KL28-06	149.9	152.8	0.0036		36	0.05	18.6	4240	7100	7	8	0.01	1	10.8	4.0	17	0.01
KL28-06	152.8	155.1	0.002		20	0.03	3.5	530	1110	8	7	0.01	1	1.5	2.3	18	0.01
KL28-06	155.1	157.5	0.0037		37	0.03	4.5	1690	2370	8	13	0.01	1	2.9	2.8	17	0.01
KL28-06	157.5	160.5	0.0029		29	0.04	4.4	1020	1630	8	6	1	2	1.7	3.3	27	0.01
KL28-06	160.5	163.5	0.0035		35	0.03	4.9	910	1250	7	7	0.01	1	2.6	3.8	29	0.01
KL28-06	163.5	166.5	0.0021		21	0.06	3.3	650	1030	6	12	0.01	2	1.4	4.3	24	0.01
KL28-06	166.5	169.5	0.0018		18	0.02	1.8	223	590	3	7	0.01	1	0.7	1.5	21	0.01
KL28-06	169.5	171	0.0017		17	0.01	2.3	490	1030	2	8	0.01	1	1	2.0	23	0.01
KL28-06	171	173.2	0.0032		32	0.03	3.9	590	1180	6	42	0.01	1	1.7	2.0	26	0.01
KL28-06	173.2	175.3	0.0027		27	0.02	2.5	470	1450	7	34	0.01	2	1.5	2.8	24	0.01
KL28-06	175.3	178.5	0.0062		62	0.02	4.5	2120	1990	11	25	0.01	1	2.7	1.0	35	0.01
KL28-06	178.5	181.5	0.0039		39	0.02	4	2540	1850	5	10	0.01	1	1.8	2.0	22	0.01
KL28-06	181.5	183.5	0.0014		14	0.01	1.5	630	630	2	9	0.01	1	0.9	1.2	15	0.01
KL28-06	183.5	185.9	0.0012		12	0.01	3.3	470	500	7	10	0.01	1	1.7	3.0	16	0.01
KL28-06	185.9	187.5	0.0042		42	0.01	5.6	1750	1320	5	4	0.01	1	3.5	3.8	10	0.01
KL28-06	187.5	190.5	0.0075		75	0.03	3.8	770	1780	10	18	3	1	2.3	12.3	10	0.01
KL28-06	190.5	193.5	0.0268		268	0.01	6.8	6740	3460	8	6	0.01	1	9.2	4.0	8	0.01
KL28-06	193.5	196.5	0.0038		38	0.01	3.8	590	770	7	14	0.01	2	1	3.5	13	0.01
KL28-06	196.5	199.3	0.0039		39	0.01	2.4	660	950	4	12	1	1	1.3	4.0	14	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL28-06	199.3	201.5	0.0054	54	0.01	4.6	1530	1760	6	7	1	1	2.2	8.2	10	0.01
KL28-06	201.5	204	0.0016	16	0.01	1.3	62	880	2	2	0.01	1	0.8	2.0	12	0.01
KL28-06	204	207	0.0029	29	0.01	2.8	1900	1680	6	4	0.01	1	2.2	5.0	8	0.01
KL28-06	207	210	0.0062	62	0.02	1.4	1140	800	3	6	0.01	3	1.1	3.5	12	0.01
KL28-06	210	211.5	0.0069	69	0.03	3	1510	2000	15	31	1	4	1.8	9.5	14	0.01
KL28-06	211.5	213.8	0.0058	58	0.02	3.8	3270	2680	11	14	2	1	2.3	7.5	10	0.1
KL28-06	213.8	216.5	0.0218	218	0.05	28	35400	32900	23	6	12	2	30	19.5	11	0.42
KL28-06	216.5	218.8	0.005	50	0.02	4.4	4000	4770	7	6	5	1	2.3	5.5	8	0.01
KL28-06	218.8	221.8	0.0025	25	0.03	1.8	1040	1430	2	52	4	1	0.01	2.8	8	0.01
KL28-06	221.8	225.7	0.0023	23	0.03	1.5	690	1320	3	35	4	1	0.4	2.5	14	0.01
KL28-06	225.7	228	0.0017	17	0.02	0.6	750	590	3	6	1	1	0.5	2.2	10	0.01
KL28-06	228	230.8	0.06	600	0.29	57	105000	66900	37	43	32	1	74	40.0	12	1.24
KL28-06	230.8	232.2	0.0038	38	0.04	5.8	3060	3780	10	20	9	1	2.5	4.8	10	0.14
KL28-06	232.2	234.7	0.0055	55	0.05	3.5	6760	4920	15	8	5	1	8.7	6.2	19	0.11
KL28-06	234.7	236.2	0.0129	129	0.05	1.2	1650	480	24	6	3	1	4.7	6.5	15	0.01
KL28-06	236.2	239.2	0.048	480	0.16	10.9	8700	4900	120	7	39	1	11.1	8.5	18	0.38
KL28-06	239.2	241.3	0.041	410	0.19	7.6	3000	1600	120	4	30	1	7	6.3	20	0.18
KL28-06	241.3	244.5	0.0115	115	0.11	4.3	1310	820	20	2	30	1	2.5	6.2	19	0.01
KL28-06	244.5	247.5	0.066	660	0.17	2	1730	201	22	9	14	1	0.8	6.0	17	0.1
KL28-06	247.5	250.5	0.057	570	0.17	7.7	2940	1460	23	6	25	1	1.8	11.5	20	0.01
KL28-06	250.5	253.5	0.017	170	0.14	9.6	5070	3770	18	20	18	1	4.4	17.8	21	0.11
KL28-06	253.5	256.5	0.0099	99	0.13	4.1	2440	1700	22	15	5	1	4.8	6.8	11	0.01
KL28-06	256.5	259.5	0.0094	94	0.04	3.1	1640	1120	19	26	4	1	2.6	5.8	16	0.01
KL28-06	259.5	262.5	0.0347	347	0.12	4.2	6700	1900	35	6	19	6	3.2	15.0	14	0.01
KL28-06	262.5	264	0.0189	189	0.05	3.1	1470	2770	8	36	13	1	1.7	14.4	14	0.01
KL28-06	264	267	0.185	1850	0.24	2.5	2900	590	15	7	6	12	1.2	7.3	14	0.01
KL28-06	267	270	0.36	3600	0.49	1.6	20700	134	22	33	2	64	2.1	13.3	22	0.01
KL28-06	270	273	0.127	1270	0.19	0.9	1650	168	9	14	1	23	1.9	6.8	32	0.01
KL28-06	273	274.5	0.181	1810	0.2	0.1	710	83	1	6	0.01	21	1.3	5.5	20	0.01
KL28-06	274.5	277.5	0.58	5800	1.09	22.6	47300	23000	46	241	12	30	21	13.7	65	0.16
KL28-06	277.5	280.5	0.135	1350	0.29	1.1	1420	114	19	2930	3	9	0.8	12.3	74	0.01
KL28-06	280.5	283.5	0.085	850	0.2	0.9	324	170	5	1080	2	6	0.4	5.8	75	0.01
KL28-06	283.5	286.5	0.392	3920	0.36	2.2	383	112	9	1360	3	28	0.5	12.5	47	0.01
KL28-06	286.5	289.5	0.27	2700	0.44	2.2	1460	277	29	100	4	17	1.9	17.3	62	0.01
KL28-06	289.5	292.5	0.145	1450	0.19	1.5	1090	69	8	670	7	16	0.7	14.3	75	0.01
KL28-06	292.5	294	0.55	5500	1.02	6.2	16200	124	22	1700	17	45	0.8	20.5	51	0.01
KL28-06	294	297	0.078	780	0.44	2	3310	970	28	1950	6	11	2.7	17.8	42	0.01
KL28-06	297	300	1.36	13600	2.24	14.8	3500	340	29	505	5	85	1.6	28.5	44	0.01
KL28-06	300	303	0.118	1180	0.42	1.4	290	81	9	2650	3	12	0.5	9.4	34	0.01
KL28-06	303	306	0.56	5600	0.85	3.6	2140	262	16	810	3	47	0.3	19.0	107	0.01
KL28-06	306	308.7	1.07	10700	1.65	5.1	890	157	8	500	4	65	0.3	17.2	127	0.01
KL28-06	308.7	310.5	1.45	14500	0.57	5.1	1270	620	10	60	0.01	13	1	10.0	44	0.1
KL28-06	310.5	312	2.53	25300	4.78	10.6	570	53	9	164	1	90	1.1	14.5	143	0.01
KL28-06	312	315	0.189	1890	0.15	1	420	51	7	100	2	34	0.6	23.3	103	0.01
KL28-06	315	318	0.355	3550	0.52	1.7	293	87	7	311	1	35	0.3	14.5	69	0.01
KL28-06	318	321	0.66	6600	0.64	4.7	17600	53	12	710	6	106	0.3	20.8	34	0.15
KL28-06	321	324	1.02	10200	2.4	10.5	23400	24	19	184	3	54	0.9	29.0	39	0.01
KL28-06	324	327	0.32	3200	0.57	2.9	46000	44	7	9	4	45	1.2	28.0	42	0.01
KL28-06	327	330	0.166	1660	0.35	0.9	2190	20	4	10	1	36	0.3	4.0	48	0.01
KL28-06	330	333	0.57	5700	4.52	7.4	1330	26	3	36	2	58	0.3	11.3	38	0.01
KL28-06	333	336	0.7	7000	1.5	3	384	17	8	5	1	54	0.01	14.5	29	0.01
KL28-06	336	339	1.74	17400	1.08	9.7	1370	24	7	40	4	141	0.2	20.5	25	0.01
KL28-06	339	342	1.33	13300	0.88	4	580	19	2	126	4	175	0.5	30.0	34	0.01
KL28-06	342	345	3.45	34500	3.24	10	1060	30	3	27	5	250	1.1	34.0	42	0.01
KL28-06	345	347.7	0.79	7900	0.63	2.9	470	410	3	20	2	65	1.1	12.3	24	0.01
KL28-06	347.7	349.1	6.37	63700	3.39	182	1410	1900	17	90	2	75	6.4	12.5	33	0.14
KL28-06	349.1	351.4	9.04	90400	3.27	21.8	760	249	2	4	3	60	0.4	8.8	28	0.01
KL28-06	351.4	354	5.3	53000	3.43	7.6	178	17	0.01	3	2	40	0.2	26.0	28	0.01
KL28-06	354	357	3.45	34500	1.72	6	143	18	0.01	5	7	38	0.2	23.0	25	0.01
KL28-06	357	360	2.76	27600	1.21	5.4	138	13	0.01	10	2	48	0.2	25.0	17	0.01
KL28-06	360	362.5	1.72	17200	0.72	3.1	172	13	10	120	0.01	23	0.01	15.0	41	0.01
KL28-06	362.5	365.4	0.75	7500	0.43	0.9	54	14	0.01	321	1	8	0.2	5.8	58	0.01
KL28-06	365.4	367.6	0.331	3310	0.15	1	71	8	2	23	0.01	5	0.01	3.3	72	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL28-06	367.6	369	3.05	30500	1.23	4.5	1840	670	19	70	1	20	0.7	8.0	57	0.01
KL28-06	369	372	1	10000	1.15	4.8	1420	430	47	50	0.01	9	2.1	7.5	75	0.01
KL28-06	372	375	1.49	14900	0.63	2.1	78	24	1	290	0.01	16	0.01	8.5	84	0.01
KL28-06	375	378	1.08	10800	0.62	2	52	21	2	173	0.01	11	0.01	6.5	78	0.01
KL28-06	378	381	1.19	11900	0.57	2.2	60	15	1	504	1	18	0.01	7.5	73	0.01
KL28-06	381	384	1.44	14400	0.7	2.5	38	13	1	186	0.01	10	0.01	7.5	62	0.01
KL28-06	384	387	1.16	11600	0.9	2	49	10	1	265	1	11	0.01	7.5	83	0.01
KL28-06	387	390	0.98	9800	0.48	1.8	67	9	1	107	0.01	14	0.01	5.5	79	0.01
KL28-06	390	393	0.95	9500	0.43	1.3	50	5	1	51	0.01	12	0.01	6.0	70	0.01
KL28-06	393	396	1.05	10500	1.15	5.8	2400	550	21	23	7	8	0.2	10.8	47	0.01
KL28-06	396	399	1.28	12800	0.75	2.4	103	33	3	20	1	12	0.01	7.3	75	0.01
KL28-06	399	402	1.43	14300	0.9	2	54	14	9	180	1	11	0.4	9.5	68	0.01
KL28-06	402	405	0.93	9300	0.53	1.8	53	16	2	58	0.01	9	0.2	6.5	75	0.01
KL28-06	405	408	0.82	8200	0.71	2.4	104	30	1	137	0.01	18	0.3	9.3	87	0.01
KL28-06	408	411	0.98	9800	0.59	2.3	51	9	1	100	2	12	0.01	5.8	75	0.01
KL28-06	411	414	0.94	9400	0.43	2.1	71	6	1	141	0.01	14	0.01	4.8	68	0.01
KL28-06	414	417	1.08	10800	0.72	2.5	72	11	1	170	1	17	0.01	5.0	70	0.01
KL28-06	417	420	1.39	13900	1.02	3.3	53	9	1	73	1	15	0.01	9.0	71	0.01
KL28-06	420	423	1.81	18100	1.49	3.4	49	9	1	173	1	14	0.01	8.0	60	0.01
KL28-06	423	426	1.07	10700	0.37	6.3	84	182	17	59	7	17	1.1	6.5	56	0.01
KL28-06	426	429	1.32	13200	0.3	5.9	71	62	8	119	7	14	1.4	10.0	36	0.01
KL28-06	429	432	0.61	6100	0.22	1.9	53	11	2	65	2	10	0.01	5.5	52	0.01
KL28-06	432	435	0.338	3380	0.16	0.9	44	10	2	27	0.01	7	0.01	3.5	53	0.01
KL28-06	435	438	0.321	3210	0.14	0.8	104	12	1	27	0.01	6	0.01	3.0	62	0.01
KL28-06	438	441	0.313	3130	0.18	1.1	95	27	7	27	0.01	6	0.3	3.0	69	0.01
KL28-06	441	443.3	0.74	7400	0.21	5.8	72	45	10	72	2	5	1	4.0	46	0.01
KL28-06	443.3	445.6	0.72	7200	0.32	1.9	74	13	6	34	0.01	12	0.01	7.6	85	0.01
KL28-06	445.6	447	0.58	5800	0.32	1.7	73	12	6	91	1	12	0.01	4.2	81	0.01
KL28-06	447	450	0.7	7000	0.34	1.2	65	11	2	14	0.01	13	0.01	6.2	56	0.01
KL28-06	450	453	0.265	2650	0.24	1.4	43	22	0.01	18	0.01	8	0.01	4.0	87	0.01
KL28-06	453	456	0.34	3400	0.17	1.7	398	167	8	71	2	6	0.7	3.5	83	0.01
KL28-06	456	459	0.64	6400	0.25	2.3	470	225	11	36	1	6	4.8	7.5	202	0.01
KL28-06	459	462	0.59	5900	0.19	2.2	181	85	8	100	1	6	2.3	5.0	117	0.01
KL28-06	462	465	0.565	5650	0.1	3.2	219	127	16	26	10	6	3	5.8	161	0.01
KL28-06	465	468	0.66	6600	0.16	4.2	87	59	10	10	10	3	4.2	3.5	151	0.01
KL28-06	468	471	0.5	5000	0.21	2	240	108	13	16	3	4	2.1	4.2	202	0.01
KL28-06	471	474	0.49	4900	0.51	0.7	38	11	2	17	0.01	5	0.01	4.5	170	0.01
KL28-06	474	477	0.71	7100	0.46	1.6	140	38	460	25	1	6	2.2	5.2	170	0.01
KL28-06	477	480	0.67	6700	0.36	3.6	70	47	42	17	3	6	6.5	5.7	156	0.01
KL28-06	480	483	0.51	5100	0.52	2.8	90	15	830	13	5	6	3.9	6.2	160	0.01
KL28-06	483	486	0.83	8300	0.22	5.2	35	17	540	50	5	8	1.7	9.1	161	0.01
KL28-06	486	489	0.32	3200	0.1	0.1	304	88	20	27	0.01	2	0.8	4.5	50	0.01
KL28-06	489	492	0.57	5700	0.16	1.2	40	14	8	24	1	3	0.01	5.5	51	0.01
KL28-06	492	495	0.56	5600	0.31	1.1	43	18	8	22	0.01	4	0.01	5.7	281	0.01
KL28-06	495	498	0.35	3500	0.2	0.7	45	18	6	8	0.01	3	0.2	4.5	250	0.01
KL28-06	498	501	0.31	3100	0.06	0.1	65	40	13	46	0.01	5	0.9	2.8	267	0.01
KL28-06	501	504	0.27	2700	0.05	0.8	450	87	7	26	0.01	5	0.7	4.5	201	0.01
KL28-06	504	507	0.27	2700	0.05	0.7	283	60	4	57	1	4	0.01	4.7	154	0.01
KL28-06	507	510	0.62	6200	0.14	1.5	121	50	4	20	2	5	0.01	5.0	254	0.01
KL28-06	510	513	0.474	4740	0.12	1.6	133	69	4	51	0.01	6	0.5	5.1	175	0.01
KL28-06	513	516	0.377	3770	0.1	1.5	88	50	3	25	0.01	3	1.1	5.0	141	0.01
KL28-06	516	519	0.408	4080	0.19	1	110	46	3	34	1	4	0.01	4.7	211	0.01
KL28-06	519	522	0.65	6500	0.55	1.6	41	16	4	27	1	5	0.01	4.9	260	0.01
KL28-06	522	525	0.68	6800	0.32	1.3	50	21	5	30	0.01	3	0.3	5.3	180	0.01
KL28-06	525	528	0.492	4920	0.16	2.2	123	90	10	24	6	2	1.4	11.6	157	0.01
KL28-06	528	531	0.51	5100	0.14	2	43	28	11	28	2	3	1.3	4.0	217	0.01
KL28-06	531	534	0.94	9400	0.3	2.8	108	51	6	32	7	6	1.5	10.3	96	0.01
KL28-06	534	537	0.84	8400	0.32	2.8	61	25	4	32	3	8	0.4	6.5	274	0.01
KL28-06	537	540	0.442	4420	0.25	1.4	57	16	2	60	0.01	7	0.2	6.0	212	0.01
KL28-06	540	543	0.5	5000	0.4	1.4	188	47	1	102	1	4	0.2	4.3	160	0.01
KL28-06	543	546	0.71	7100	0.56	2	105	35	2	62	2	9	0.2	4.7	191	0.01
KL28-06	546	549	0.9	9000	0.65	1.8	54	16	2	57	1	10	0.3	5.0	167	0.01
KL28-06	549	552	0.68	6800	0.54	2	246	212	1	48	1	6	0.01	4.8	271	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL28-06	552	555	0.44	4400	0.26	1.6	51	16	1	21	1	4	0.01	4.5	164	0.01
KL28-06	555	558	0.57	5700	0.23	2.6	20	46	8	30	4	10	1.7	14.9	222	0.01
KL28-06	558	561	0.53	5300	0.12	2.1	217	46	5	20	2	6	1.2	6.5	156	0.01
KL28-06	561	564	0.57	5700	0.09	2.3	81	40	5	30	3	4	0.01	4.8	186	0.01
KL28-06	564	567	0.053	530	0.07	0.1	36	26	12	28	2	5	2.5	9.1	95	0.01
KL28-06	567	570	0.393	3930	0.13	1.2	60	31	5	28	2	7	0.9	6.7	100	0.01
KL28-06	570	573	0.387	3870	0.22	1.6	32	39	26	42	3	5	6.2	9.0	123	0.01
KL28-06	573	576	0.29	2900	0.12	1.1	65	35	9	18	3	8	2.8	11.6	91	0.01
KL28-06	576	579	0.411	4110	0.1	1.9	151	60	4	8	2	7	0.9	6.1	122	0.01
KL28-06	579	582	0.57	5700	0.11	2.1	112	64	3	17	2	5	2.3	5.8	141	0.01
KL28-06	582	585	0.448	4480	0.13	1.6	166	70	2	14	1	3	0.4	6.0	101	0.01
KL28-06	585	588	0.35	3500	0.16	1.3	352	116	0.01	12	1	4	0.2	5.8	163	0.01
KL28-06	588	591	0.47	4700	0.17	2	1150	750	22	13	0.01	6	0.3	5.6	150	0.01
KL28-06	591	594	0.57	5700	0.17	1.6	342	168	4	24	1	10	0.8	6.5	110	0.01
KL28-06	594	596.8	0.62	6200	0.24	2.1	1060	138	3	10	0.01	11	0.2	6.5	110	0.01
KL28-06	596.8	599.4	0.65	6500	0.16	2.1	880	239	2	9	1	7	0.2	4.1	155	0.01
KL28-06	599.4	602.5	0.23	2300	0.06	1.8	2110	368	9	25	1	5	0.4	4.3	105	0.01
KL28-06	602.5	605.6	0.28	2800	0.07	1.8	1640	440	14	19	2	7	0.5	3.5	120	0.01
KL28-06	605.6	608.7	0.419	4190	0.11	2.7	930	190	10	12	5	4	0.7	6.0	101	0.01
KL28-06	608.7	611.8	0.509	5090	0.27	3.2	800	710	13	12	4	7	0.5	7.0	152	0.01
KL28-06	611.8	613.3	0.23	2300	0.07	1.3	284	65	12	12	2	5	0.2	3.5	159	0.01
KL28-06	613.3	615	0.235	2350	0.04	1.5	232	80	2	13	2	5	0.2	3.9	140	0.01
KL28-06	615	618	0.25	2500	0.05	1.5	283	74	3	13	2	5	0.3	2.3	115	0.01
KL28-06	618	621	0.48	4800	0.07	2	630	143	5	19	3	7	0.3	4.8	110	0.01
KL28-06	621	624	0.95	9500	0.17	2.7	880	165	4	16	4	7	0.2	4.2	156	0.01
KL28-06	624	627	0.53	5300	0.14	2.8	4940	2440	440	28	3	10	7.6	8.5	98	0.01
KL28-06	627	630	0.61	6100	0.22	2	257	59	7	14	1	9	0.2	6.7	131	0.01
KL28-06	630	633	0.34	3400	0.1	1.9	410	173	0.01	11	1	6	0.2	3.3	85	0.01
KL28-06	633	636	0.33	3300	0.11	1.8	267	180	5	10	2	9	0.2	6.7	77	0.01
KL28-07	0	3	0.005	50	0.05	0.1	138	62	20	2	0.01	1	2.7	1.9	31	0.01
KL28-07	3	6	0.0024	24	0.03	0.1	41	23	9	3	0.01	2	0.6	3.5	27	0.01
KL28-07	6	9	0.0027	27	0.04	0.8	108	95	26	4	2	3	0.9	3.3	35	0.1
KL28-07	9	12	0.002	20	0.02	0.1	59	77	4	1	0.01	1	0.4	0.6	18	0.01
KL28-07	12	15	0.0035	35	0.06	0.7	196	178	8	1	0.01	1	0.9	1.3	25	0.01
KL28-07	15	18	0.0024	24	0.05	0.6	280	355	15	4	2	1	3.3	2.0	22	0.01
KL28-07	18	20.9	0.0009	9	0.02	0.9	258	670	8	1	1	1	0.9	1.6	19	0.01
KL28-07	20.9	24	0.0034	34	0.03	1.3	254	580	11	2	2	1	1.2	2.5	21	0.01
KL28-07	24	27	0.0022	22	0.1	2.3	230	335	14	10	6	1	5.2	15.8	43	0.01
KL28-07	27	30	0.0026	26	0.07	1.8	347	600	22	15	5	1	1.5	11.0	28	0.01
KL28-07	30	33	0.0063	63	0.03	9.6	2900	3140	43	16	47	1	1.1	107.5	47	0.01
KL28-07	33	36	0.0197	197	0.08	55	28300	5300	53	28	320	1	2.1	220.0	53	0.01
KL28-07	36	39	0.0017	17	0.05	2	770	710	27	1	5	2	1.7	9.4	18	0.01
KL28-07	39	42	0.0013	13	0.02	0.1	220	480	15	1	0.01	3	1	3.0	17	0.01
KL28-07	42	45	0.002	20	0.06	0.1	215	309	24	1	2	1	1.2	6.3	21	0.01
KL28-07	45	48	0.0011	11	0.04	0.1	209	93	20	1	0.01	1	0.8	2.0	28	0.01
KL28-07	48	51	0.0017	17	0.01	0.1	190	83	12	1	1	1	0.6	2.5	32	0.01
KL28-07	51	54	0.0011	11	0.01	0.1	149	110	12	1	0.01	1	0.6	1.3	37	0.01
KL28-07	54	57	0.0005	5	0.01	0.1	69	35	5	1	0.01	1	0.4	1.0	29	0.01
KL28-07	57	60	0.0006	6	0.03	0.1	98	69	7	1	0.01	1	0.4	2.0	26	0.01
KL28-07	60	63	0.0009	9	0.01	0.1	89	28	4	1	0.01	1	0.4	1.3	36	0.01
KL28-07	63	66	0.001	10	0.01	0.1	184	90	3	1	0.01	1	0.3	1.8	25	0.01
KL28-07	66	69	0.001	10	0.01	0.1	68	64	4	1	0.01	1	0.2	1.3	26	0.01
KL28-07	69	72	0.0012	12	0.01	0.1	46	36	2	1	0.01	1	0.01	5.0	26	0.01
KL28-07	72	75	0.0012	12	0.01	0.1	68	51	3	1	1	1	0.3	1.6	25	0.01
KL28-07	75	78	0.0017	17	0.01	0.1	70	88	4	1	0.01	1	0.2	1.0	26	0.01
KL28-07	78	81	0.0105	105	0.01	0.9	205	87	11	1	3	1	1.2	3.8	42	0.01
KL28-07	81	84	0.0024	24	0.01	0.6	93	40	4	3	3	1	1.1	5.0	71	0.01
KL28-07	84	87	0.0078	78	0.07	5.7	124	376	12	4	40	3	1.6	51.0	81	0.01
KL28-07	87	90	0.0071	71	0.11	1.1	68	43	8	6	7	2	0.7	6.5	116	0.01
KL28-07	90	93	0.003	30	0.02	0.6	59	111	15	5	4	3	0.9	13.0	138	0.01
KL28-07	93	94.5	0.0219	219	0.05	23.2	510	9700	20	12	49	3	2.5	27.8	112	0.01
KL28-07	94.5	96.5	0.55	5500	0.2	12.9	600	1900	46	3	74	10	4.7	59.0	41	0.01
KL28-07	96.5	99	0.107	1070	0.14	13.7	2020	1250	210	6	160	3	9.5	55.0	48	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL28-07	99	102	0.0263	263	0.16	10.1	690	3500	50	37	40	13	1.7	16.5	74	0.01
KL28-07	102	105	0.009	90	0.13	6.5	237	10300	17	14	2	1	2.8	2.9	115	0.01
KL28-07	105	108	0.026	260	0.12	9.8	830	7200	25	7	24	3	6.3	3.0	35	0.01
KL28-07	108	111	0.0051	51	0.05	3.6	261	1250	8	28	13	1	1.7	1.5	119	0.01
KL28-07	111	114	0.0014	14	0.02	2.1	117	1010	10	8	4	1	1.8	0.7	78	0.01
KL28-07	114	117	0.0025	25	0.04	4	112	1880	6	6	8	1	2.9	0.8	132	0.01
KL28-07	117	118.5	0.0132	132	0.04	2.8	138	1070	11	8	6	1	1.8	1.5	106	0.01
KL28-07	118.5	121	0.0253	253	0.02	1.7	118	650	12	9	3	1	1.6	0.8	96	0.01
KL28-07	121	123	0.0032	32	0.07	5.8	203	1450	16	16	9	1	5.5	6.0	105	0.01
KL28-07	123	125	0.0059	59	0.03	3.9	158	950	21	10	7	1	5	2.9	77	0.01
KL28-07	125	127.5	0.0256	256	0.04	1.1	285	425	10	10	4	1	1.9	5.5	124	0.01
KL28-07	127.5	130.5	0.0325	325	0.03	1	171	162	8	8	3	1	1.9	3.0	102	0.01
KL28-07	130.5	133.5	0.0054	54	0.02	0.8	198	220	7	13	4	1	1.3	3.5	110	0.01
KL28-07	133.5	136.5	0.0129	129	0.01	0.6	102	153	4	7	2	1	1.3	3.3	67	0.01
KL28-07	136.5	139.5	0.0068	68	0.02	0.8	94	139	9	20	3	2	0.9	4.0	49	0.01
KL28-07	139.5	142.5	0.0109	109	0.02	1.8	138	590	12	640	12	1	1.4	15.8	52	0.01
KL28-07	142.5	145.5	0.0119	119	0.02	30.2	2360	7000	46	13	143	3	4.4	8.5	17	0.01
KL28-07	145.5	147	0.067	670	0.03	59	8000	11700	34	146	211	7	2.3	35.5	22	0.01
KL28-07	147	150	0.0043	43	0.01	2	410	510	30	9	0.01	1	1.9	1.3	13	0.01
KL28-07	150	153	0.166	1660	0.13	67	18000	11800	190	61	6	1	45	27.0	34	0.21
KL28-07	153	156	0.0221	221	0.04	18.9	3130	2820	24	10	26	2	3.6	6.3	27	0.01
KL28-07	156	158.3	0.0059	59	0.01	5	1640	2000	21	8	2	1	2.4	3.3	17	0.01
KL28-07	158.3	160.5	0.091	910	0.08	82	14800	45500	48	12	7	1	90	28.0	20	0.32
KL28-07	160.5	163.5	0.0086	86	0.02	5.3	940	1150	17	5	1	1	4.1	2.8	16	0.01
KL28-07	163.5	166.5	0.0158	158	0.03	5.7	3860	4100	11	9	2	1	4.2	4.8	19	0.01
KL28-07	166.5	169.5	0.0067	67	0.02	5.5	1620	2340	5	10	8	1	1.1	3.3	19	0.01
KL28-07	169.5	172.5	0.0084	84	0.02	11.1	1420	2830	10	29	23	1	1.6	4.8	17	0.01
KL28-07	172.5	175.5	0.0093	93	0.06	6.2	2900	8600	13	26	2	1	3.8	4.5	22	0.01
KL28-07	175.5	178.5	0.0363	363	0.02	3.3	1930	3320	4	11	4	1	1.8	5.8	21	0.01
KL28-07	178.5	180	0.0165	165	0.03	7.2	2820	6600	13	8	10	1	6.4	8.6	21	0.01
KL28-07	180	183	0.0092	92	0.01	0.1	209	317	3	16	0.01	1	0.6	1.2	20	0.01
KL28-07	183	186	0.0168	168	0.06	1.5	1360	2720	9	45	0.01	1	1.6	3.0	23	0.01
KL28-07	186	189	0.0164	164	0.06	1.9	2180	4580	14	34	2	1	2.5	4.5	22	0.01
KL28-07	189	192	0.0359	359	0.07	2.8	4390	5800	74	87	3	1	4.1	11.4	30	0.01
KL28-07	192	195	0.0248	248	0.02	1.2	540	1410	33	79	5	1	0.5	3.0	21	0.01
KL28-07	195	198	0.0087	87	0.02	0.6	369	1630	8	69	1	1	0.5	2.0	20	0.01
KL28-07	198	201	0.0121	121	0.01	0.9	490	2060	11	85	3	3	0.5	3.8	22	0.01
KL28-07	201	204	0.0324	324	0.04	2.6	1420	4270	52	107	10	1	2.8	4.3	22	0.01
KL28-07	204	207	0.0263	263	0.03	2.7	1570	2180	68	42	7	3	4	3.0	23	0.01
KL28-07	207	210	0.0097	97	0.05	2	1060	2280	17	163	6	1	2.1	2.4	29	0.01
KL28-07	210	213	0.018	180	0.03	1.8	870	1720	28	127	7	1	1.7	1.8	23	0.01
KL28-07	213	216	0.0187	187	0.02	3.8	1690	2970	39	117	13	1	3.8	3.0	22	0.01
KL28-07	216	219	0.0111	111	0.01	7.1	2830	5300	10	60	11	1	5.3	9.1	13	0.01
KL28-07	219	222	0.0076	76	0.01	2.4	1030	1500	12	49	2	1	3.9	2.8	10	0.01
KL28-07	222	225	0.0073	73	0.01	1.2	470	680	12	28	2	1	2	1.8	13	0.01
KL28-07	225	228	0.049	490	0.03	3.9	1870	2830	17	50	7	1	3.7	3.8	16	0.01
KL28-07	228	231	0.0096	96	0.01	1.2	690	640	14	53	5	1	1	2.3	16	0.01
KL28-07	231	234	0.017	170	0.04	0.1	610	322	9	79	2	2	1	1.8	22	0.01
KL28-07	234	237	0.041	410	0.15	1.6	1480	227	27	11	20	4	2.3	11.5	37	0.01
KL28-07	237	240	0.121	1210	0.22	12.2	8400	16000	53	72	54	3	2.7	110.0	36	0.01
KL28-07	240	241.5	0.08	800	0.12	6	4300	5100	18	8	54	3	1.8	39.3	24	0.01
KL28-07	241.5	244.5	0.044	440	0.13	6.7	7100	7700	12	11	115	4	1.6	40.0	25	0.01
KL28-07	244.5	247.5	0.0222	222	0.39	1.5	2700	145	6	4	19	3	1.3	5.4	15	0.01
KL28-07	247.5	249	0.07	700	0.24	7	14900	9100	33	13	135	5	6.3	60.4	33	0.01
KL28-07	249	252	0.061	610	0.48	3.5	14500	213	9	2	100	6	3.4	17.5	33	0.01
KL28-07	252	253.5	0.0164	164	0.11	0.1	1420	77	5	2	3	3	0.4	4.9	22	0.01
KL28-07	253.5	256.5	0.0378	378	0.07	0.1	2800	70	7	8	2	5	0.8	4.0	21	0.01
KL28-07	256.5	258	0.0099	99	0.02	0.1	2010	46	6	7	1	5	0.4	4.3	19	0.01
KL28-07	258	261	0.0234	234	0.04	0.1	7000	21	6	3	0.01	10	3.4	8.0	20	0.01
KL28-07	261	264	0.0046	46	0.02	0.1	740	23	5	2	0.01	5	1.1	3.3	13	0.01
KL28-07	264	267	0.067	670	0.12	0.1	16100	70	9	3	2	15	1.8	11.3	14	0.01
KL28-07	267	270	0.8	8000	0.93	3.5	34000	52	13	6	4	128	2.6	24.7	29	0.01
KL28-07	270	274.5	0.87	8700	0.88	2.1	5400	118	1	30	1	49	1.1	11.0	27	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL28-07	274.5	277.5	1.51	15100	1.83	4	9900	93	4	32	7	60	0.4	34.5	25	0.01
KL28-07	277.5	280.5	0.83	8300	0.93	2.3	7100	90	4	10	5	58	2.4	12.3	30	0.01
KL28-07	280.5	283.5	0.113	1130	0.2	0.8	28700	60	5	6	1	93	4.4	15.3	25	0.01
KL28-07	283.5	286.5	0.307	3070	0.35	1.3	12900	35	19	5	1	48	3.7	10.5	26	0.01
KL28-07	286.5	288	1.07	10700	1.32	1.7	2900	37	4	44	1	45	1.4	9.3	20	0.01
KL28-07	288	291	0.91	9100	1.79	3.6	6600	124	6	550	4	50	1.5	18.3	33	0.01
KL28-07	291	294	0.61	6100	0.83	4.3	13800	116	17	77	2	33	0.5	33.0	24	0.01
KL28-07	294	297	0.68	6800	0.86	5.8	36400	195	31	540	1	41	2.8	43.2	32	0.01
KL28-07	297	300	0.074	740	0.13	0.1	143	40	32	430	1	5	0.3	6.0	70	0.01
KL28-07	300	303	0.127	1270	0.27	1	162	54	18	3010	3	7	0.2	9.3	66	0.01
KL28-07	303	306	0.106	1060	0.25	0.9	640	96	13	1350	4	9	0.3	6.6	36	0.01
KL28-07	306	309	0.21	2100	0.35	0.9	2900	135	8	1590	3	13	0.3	10.3	37	0.01
KL28-07	309	312	0.37	3700	1.58	3.4	5200	126	9	32	6	68	0.7	47.9	32	0.01
KL28-07	312	315	0.88	8800	2.06	20.6	10000	9200	6	324	106	104	1.6	96.8	33	0.01
KL28-07	315	318	0.153	1530	0.48	1.7	65800	105	10	63	2	57	0.7	39.8	27	0.01
KL28-07	318	321	0.95	9500	1.94	6.1	51200	132	14	940	4	80	0.5	19.8	48	0.01
KL28-07	321	324	0.2	2000	0.42	1.6	5900	63	5	224	0.01	15	0.3	11.8	30	0.01
KL28-07	324	327	0.077	770	0.29	0.6	860	105	17	1270	1	8	0.4	5.3	45	0.01
KL28-07	327	330	0.37	3700	1.27	1.7	28100	96	9	129	1	73	0.6	15.0	41	0.01
KL28-07	330	333	1.67	16700	7.63	6.5	2150	54	7	530	1	64	0.2	18.3	39	0.01
KL28-07	333	336	0.057	570	0.24	0.1	212	81	24	780	1	10	0.2	6.3	32	0.01
KL28-07	336	338.2	0.098	980	0.37	0.6	97	30	30	490	1	6	0.2	2.8	28	0.01
KL28-07	338.2	339.8	0.4	4000	1.39	1.9	1030	63	44	280	2	41	0.3	9.8	34	0.01
KL28-07	339.8	342	0.65	6500	1.68	4.3	3100	159	18	236	3	65	0.5	10.5	40	0.01
KL28-07	342	345	0.37	3700	0.67	1.9	3300	126	4	44	2	55	0.3	25.0	43	0.01
KL28-07	345	348	0.41	4100	0.6	2	780	85	2	19	4	103	0.2	12.3	51	0.01
KL28-07	348	351	0.64	6400	1.52	3.4	830	196	4	9	3	117	0.8	16.8	45	0.01
KL28-07	351	354	0.95	9500	1.9	4.7	630	124	2	17	1	104	0.5	11.8	35	0.01
KL28-07	354	357	1.36	13600	1.54	5.2	530	294	2	176	1	78	0.4	14.0	24	0.01
KL28-07	357	360	2.35	23500	1.58	3.4	430	46	1	295	0.01	67	0.4	12.0	19	0.01
KL28-07	360	363	1.9	19000	1.32	3.1	354	72	2	54	0.01	64	0.4	18.0	23	0.01
KL28-07	363	366	1.64	16400	1.52	2.3	281	33	0.01	4	0.01	50	0.3	20.0	16	0.01
KL28-07	366	369	2.27	22700	1.4	3.6	385	39	2	83	0.01	64	0.4	16.0	23	0.01
KL28-07	369	372	1.01	10100	1.28	2.3	220	20	0.01	153	0.01	45	0.3	3.9	31	0.01
KL28-07	372	375	1.07	10700	0.88	1.6	600	35	0.01	990	0.01	32	0.2	5.8	24	0.01
KL28-07	375	378	1.24	12400	0.89	2.1	270	27	0.01	308	0.01	40	0.2	14.5	25	0.01
KL28-07	378	381	0.65	6500	0.51	1.3	179	29	0.01	144	0.01	41	0.3	7.0	19	0.01
KL28-07	381	384	0.73	7300	0.55	1.2	210	35	0.01	590	0.01	43	0.01	6.5	17	0.01
KL28-07	384	387	2.42	24200	0.76	2.4	263	16	0.01	323	0.01	54	0.01	16.0	24	0.01
KL28-07	387	390	2.86	28600	1.62	4.7	181	12	1	15	1	38	0.01	16.0	24	0.01
KL28-07	390	391.6	4.4	44000	5.36	14.5	144	18	1	8	6	40	0.01	30.0	27	0.01
KL28-07	391.6	393.7	4.18	41800	33	14.4	157	12	1	50	8	40	0.01	17.5	38	0.01
KL28-07	393.7	396	3.7	37000	1.95	2.6	163	22	3	17	0.01	29	0.01	11.0	57	0.01
KL28-07	396	399	0.73	7300	0.65	1.1	273	20	2	140	0.01	13	0.2	3.5	71	0.01
KL28-07	399	402	1.24	12400	0.69	3.8	185	39	5	187	1	10	0.4	8.5	55	0.01
KL28-07	402	405	0.58	5800	0.28	1.1	104	13	2	215	0.01	10	0.01	6.3	45	0.01
KL28-07	405	408	0.98	9800	0.89	4.7	1760	200	170	213	3	14	9.6	12.0	159	0.01
KL28-07	408	411	1.1	11000	0.5	2.8	154	52	27	219	2	10	0.9	4.8	101	0.01
KL28-07	411	414	1.64	16400	1.13	2.8	80	27	7	131	3	15	0.4	10.5	80	0.01
KL28-07	414	417	1.61	16100	1.21	2.7	114	41	1	56	1	13	0.01	8.0	63	0.01
KL28-07	417	420	1.53	15300	0.71	2.2	154	29	2	158	0.01	15	0.01	7.0	67	0.01
KL28-07	420	423	1.84	18400	0.89	2.3	115	15	0.01	81	0.01	18	0.01	7.0	85	0.01
KL28-07	423	426	1.49	14900	0.75	2.2	96	12	0.01	24	0.01	14	0.01	6.5	77	0.01
KL28-07	426	429	1.12	11200	0.49	2.3	460	30	2	75	1	15	0.01	6.0	82	0.01
KL28-07	429	432	1.21	12100	0.53	2	106	18	1	150	0.01	15	0.01	8.0	78	0.01
KL28-07	432	435	1.27	12700	0.49	2.4	106	20	1	380	0.01	14	0.01	8.0	73	0.01
KL28-07	435	438	1.47	14700	0.67	2.1	128	30	1	133	0.01	14	0.01	7.5	85	0.01
KL28-07	438	441	1.12	11200	0.43	2.1	72	15	2	180	1	12	0.01	4.3	90	0.01
KL28-07	441	444	1.47	14700	0.36	4.1	374	260	24	100	3	20	0.6	19.0	81	0.01
KL28-07	444	447	1.32	13200	0.19	5.2	3070	1430	46	106	6	34	0.6	27.5	78	0.01
KL28-07	447	450	1.11	11100	0.12	3.4	940	630	54	130	1	17	0.8	10.5	63	0.01
KL28-07	450	453	0.83	8300	0.31	2.3	630	55	4	301	1	14	0.6	6.8	107	0.01
KL28-07	453	455.5	1.05	10500	0.51	2.1	95	39	0.01	83	1	16	0.2	5.5	85	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL28-07	455.5	457.5	1.07	10700	0.64	1.9	94	24	1	530	0.01	15	0.01	5.0	75	0.01
KL28-07	457.5	459	0.51	5100	0.4	1	640	19	1	273	1	13	0.01	3.5	69	0.01
KL28-07	459	462	0.76	7600	0.37	1.9	130	110	3	70	0.01	21	0.01	5.0	71	0.01
KL28-07	462	465	0.98	9800	0.36	2.1	95	17	1	217	0.01	26	0.01	4.5	102	0.01
KL28-07	465	468	0.8	8000	0.32	3.6	280	61	0.01	480	2	15	0.2	5.3	88	0.01
KL28-07	468	471	0.7	7000	0.4	2.2	128	121	0.01	142	0.01	16	0.01	4.8	73	0.01
KL28-07	471	474	0.75	7500	0.34	1.9	94	25	0.01	229	0.01	19	0.2	4.8	86	0.01
KL28-07	474	477	0.6	6000	0.26	1.7	87	21	0.01	80	0.01	17	0.01	6.8	84	0.01
KL28-07	477	480	0.5	5000	0.26	1.3	117	165	0.01	62	0.01	12	0.2	5.8	72	0.01
KL28-07	480	483	0.336	3360	0.14	0.8	75	17	0.01	190	0.01	10	0.01	7.0	66	0.01
KL28-07	483	486	0.54	5400	0.17	1.8	71	13	0.01	150	0.01	12	0.01	5.5	70	0.01
KL28-07	486	489	0.45	4500	0.2	1.2	72	13	0.01	108	0.01	12	0.01	3.8	54	0.01
KL28-07	489	492	0.431	4310	0.21	2.1	126	30	0.01	120	1	12	0.5	5.3	58	0.01
KL28-07	492	495	0.494	4940	0.2	1.3	184	23	0.01	140	0.01	16	0.01	6.0	63	0.01
KL28-07	495	496.9	0.459	4590	0.17	0.9	187	24	1	116	0.01	11	0.2	5.3	64	0.01
KL28-07	496.9	498.7	0.6	6000	0.2	1.7	112	18	0.01	142	0.01	12	0.2	5.3	77	0.01
KL28-07	498.7	501	0.66	6600	0.29	1.6	490	24	2	61	0.01	10	0.3	12.0	83	0.01
KL28-07	501	504	1.37	13700	0.56	7.5	397	150	12	65	35	12	2	12.5	117	0.01
KL28-07	504	507	0.89	8900	0.36	2.7	166	62	7	124	0.01	38	0.01	6.3	65	0.01
KL28-07	507	510	1.07	10700	0.5	4.3	480	42	0.01	121	1	25	0.01	22.5	70	0.01
KL28-07	510	513	1.62	16200	0.96	3.2	141	41	0.01	570	2	19	0.2	8.8	80	0.01
KL28-07	513	516	0.82	8200	0.45	2.1	73	23	0.01	94	2	6	0.5	2.8	165	0.01
KL28-07	516	519	0.79	7900	0.46	1.9	57	41	0.01	66	0.01	10	0.01	3.8	150	0.01
KL28-07	519	522	1.01	10100	0.17	2.2	76	45	3	34	3	9	0.3	10.5	165	0.01
KL28-07	522	525	0.463	4630	0.05	1.3	120	77	0.01	56	2	5	0.2	5.0	193	0.01
KL28-07	525	528	0.61	6100	0.11	1	60	27	0.01	21	1	3	0.01	3.8	201	0.01
KL28-07	528	531	0.464	4640	0.39	0.8	56	22	0.01	48	1	6	0.01	2.5	210	0.01
KL28-07	531	534	0.89	8900	0.49	3.5	130	38	0.01	47	1	14	0.2	5.5	164	0.01
KL28-07	534	537	0.52	5200	0.26	2	96	28	0.01	156	1	9	0.01	4.3	152	0.01
KL28-07	537	540	0.69	6900	0.29	2.4	287	174	5	15	1	7	0.4	3.3	149	0.01
KL28-07	540	543	0.95	9500	0.4	2.2	60	30	0.01	47	1	7	0.7	3.5	207	0.01
KL28-07	543	546	0.5	5000	0.15	1	70	38	0.01	58	1	3	0.9	4.0	70	0.01
KL28-07	546	549	0.75	7500	0.29	1.4	55	30	0.01	18	1	4	0.7	5.3	53	0.01
KL28-07	549	552	0.84	8400	0.35	1.4	31	18	0.01	16	1	4	0.5	4.4	41	0.01
KL28-07	552	555	1.03	10300	0.44	2.4	47	31	14	27	2	6	1.8	11.5	72	0.01
KL28-07	555	558	0.9	9000	0.45	1.9	67	34	0.01	38	1	5	0.4	5.3	65	0.01
KL28-07	558	561	0.8	8000	0.58	2	58	38	57	14	1	10	1.8	8.6	82	0.01
KL28-07	561	564	0.95	9500	0.45	2.6	58	25	4	26	2	4	0.6	5.0	54	0.01
KL28-07	564	567	0.94	9400	0.46	1.3	38	41	0.01	24	0.01	7	0.5	4.5	51	0.01
KL28-07	567	569.5	0.71	7100	0.41	1.2	50	25	0.01	16	0.01	7	0.4	3.5	60	0.01
KL28-07	569.5	572.5	0.84	8400	0.27	1.6	60	26	2	11	1	7	1.6	5.8	146	0.01
KL28-07	572.5	575.6	0.77	7700	0.45	1.7	85	55	0.01	20	1	6	0.5	5.3	85	0.01
KL28-07	575.6	578.7	0.466	4660	0.31	1.3	40	20	0.01	9	1	7	1.4	6.3	66	0.01
KL28-07	578.7	581.8	0.63	6300	0.44	1.9	57	30	0.01	14	0.01	6	0.3	3.5	54	0.01
KL28-07	581.8	584.9	0.66	6600	0.25	1.4	65	30	0.01	13	1	5	0.5	3.8	44	0.01
KL28-07	584.9	588	0.62	6200	0.3	1.4	91	37	4	9	0.01	6	1.4	4.5	105	0.01
KL28-07	588	591	1.04	10400	0.45	2.4	75	28	15	25	1	7	1	6.3	136	0.01
KL28-07	591	594	0.72	7200	0.18	1.5	93	17	56	6	2	3	2.6	4.8	273	0.01
KL28-07	594	597	0.8	8000	0.57	1.7	56	11	12	13	0.01	5	0.2	5.3	270	0.01
KL28-07	597	600	0.83	8300	0.76	1.6	43	12	2	44	0.01	5	0.3	5.0	334	0.01
KL28-07	600	603	0.78	7800	0.38	1.8	116	37	19	25	2	7	3.5	7.3	224	0.01
KL28-07	603	605.2	0.88	8800	0.32	1.5	79	20	33	22	1	6	0.3	4.7	286	0.01
KL28-07	605.2	608.2	0.78	7800	0.44	1.2	44	21	2	21	0.01	9	0.3	4.3	307	0.01
KL28-07	608.2	610	0.8	8000	0.35	1.5	42	13	2	39	0.01	11	0.3	4.3	126	0.01
KL28-07	610	612.4	0.81	8100	0.39	1.3	60	25	4	31	1	13	0.2	4.8	174	0.01
KL28-07	612.4	615	0.69	6900	0.33	1.6	50	23	7	12	1	3	2.8	4.3	267	0.01
KL28-07	615	618	1.04	10400	1.02	2.2	69	12	2	16	2	14	0.01	8.5	274	0.01
KL28-07	618	621	0.58	5800	0.37	1.5	145	38	23	17	1	14	0.4	6.8	292	0.01
KL28-07	621	624	0.7	7000	0.61	1.4	95	32	3	11	1	10	0.2	4.3	313	0.01
KL28-07	624	627	0.52	5200	0.31	1.1	160	65	4	18	0.01	6	0.4	3.7	86	0.01
KL28-07	627	630	0.81	8100	0.6	1.3	58	21	2	13	0.01	6	0.4	2.5	165	0.01
KL28-07	630	633	0.84	8400	0.7	1.7	58	17	2	44	1	7	1.4	5.0	256	0.01
KL28-07	633	636	0.96	9600	0.6	2.3	320	134	860	8	5	8	33	5.5	141	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL28-07	636	639	0.461		4610	0.23	1.5	113	33	16	59	1	3	1	3.0	154	0.01
KL28-07	639	642	1.01		10100	0.58	1.4	82	14	5	16	3	25	0.3	4.8	152	0.01
KL28-07	642	645	0.51		5100	0.16	1.2	61	33	15	12	1	3	2.4	4.0	147	0.01
KL28-07	645	648	0.495		4950	0.15	1.3	381	56	3	13	1	6	0.8	6.3	112	0.01
KL28-07	648	651	0.52		5200	0.38	1.1	62	34	2	22	0.01	4	0.5	3.9	129	0.01
KL28-07	651	654	0.415		4150	0.18	0.8	64	25	2	17	0.01	5	0.2	3.5	129	0.01
KL28-07	654	657	0.29		2900	0.08	0.6	96	38	5	16	0.01	3	0.4	2.3	123	0.01
KL28-07	657	660	0.069		690	0.03	0.1	34	9	2	1	0.01	7	0.01	0.0	49	0.01
KL28-07	660	663	0.26		2600	0.1	0.1	51	18	3	5	0.01	3	0.2	2.3	192	0.01
KL28-07	663	666	0.26		2600	0.13	0.5	62	27	3	8	0.01	3	0.6	2.0	75	0.01
KL28-07	666	669	0.25		2500	0.16	0.1	57	25	2	12	0.01	3	0.4	2.5	73	0.01
KL28-07	669	672	0.41		4100	0.2	0.8	43	13	1	11	0.01	4	0.2	2.8	177	0.01
KL28-07	672	675	0.63		6300	0.33	1.2	52	21	19	105	0.01	7	0.4	4.3	152	0.01
KL28-07	675	678	0.459		4590	0.23	0.6	30	14	3	11	0.01	7	0.2	2.0	155	0.01
KL28-07	678	681	0.408		4080	0.22	1.1	44	17	1	8	0.01	8	0.2	2.8	211	0.01
KL28-07	681	684	0.434		4340	0.23	1	47	26	1	20	0.01	9	0.3	5.0	242	0.01
KL28-07	684	686.5	0.482		4820	0.21	1	113	45	15	7	0.01	7	0.5	3.7	223	0.01
KL28-07	686.5	689.6	0.382		3820	0.11	0.8	108	44	18	22	2	7	1.1	4.3	193	0.01
KL28-07	689.6	692.7	0.112		1120	0.05	0.1	55	19	3	36	0.01	9	0.2	1.0	172	0.01
KL28-07	692.7	695.8	0.26		2600	0.1	1.2	77	23	2	35	0.01	5	0.8	3.3	258	0.01
KL28-07	695.8	698.9	0.295		2950	0.1	0.8	64	18	1	15	0.01	5	0.01	3.4	267	0.01
KL28-07	698.9	702	0.385		3850	0.2	1.5	83	21	4	15	0.01	8	0.3	3.5	160	0.01
KL28-07	702	705	0.24		2400	0.13	0.8	57	17	2	23	0.01	8	0.5	4.0	237	0.01
KL28-07	705	708	0.354		3540	0.13	1.2	62	18	4	9	0.01	6	0.3	3.2	205	0.01
KL28-07	708	711	0.25		2500	0.12	0.9	61	16	4	12	0.01	5	0.3	2.7	260	0.01
KL28-07	711	714	0.28		2800	0.14	1	246	73	12	21	0.01	5	0.6	3.4	191	0.01
KL28-07	714	717	0.425		4250	0.24	1.4	83	32	4	13	2	3	0.5	5.4	211	0.01
KL28-07	717	720	0.368		3680	0.27	1.2	52	22	4	15	0.01	4	0.8	3.1	210	0.01
KL28-07	720	723	0.25		2500	0.17	0.8	53	19	1	10	0.01	5	0.3	3.0	237	0.01
KL28-07	723	726	0.339		3390	0.21	1.4	270	129	5	22	1	8	0.7	3.7	158	0.01
KL28-07	726	729	0.465		4650	0.13	1.3	81	19	4	16	0.01	7	0.5	2.8	128	0.01
KL28-07	729	732	0.473		4730	0.07	1.5	88	48	35	30	1	6	0.8	8.1	126	0.01
KL28-07	732	735	0.351		3510	0.1	1.2	78	32	6	21	1	6	0.4	3.0	138	0.01
KL28-07	735	738	0.369		3690	0.17	1.8	234	335	25	58	1	8	1.3	3.9	205	0.01
KL28-08	0	2.5	0.0071		71	0.01	0.1	245	107	11	4	0.01	2	0.8	1.2	32	0.01
KL28-08	2.5	5.5	0.0034		34	0.01	0.1	67	31	7	2	0.01	1	0.3	0.8	22	0.01
KL28-08	5.5	8.2	0.0054		54	0.01	0.1	98	36	23	4	0.01	2	0.4	1.4	21	0.01
KL28-08	8.2	11.5	0.005		50	0.02	0.1	164	101	10	6	1	1	0.5	2.0	20	0.01
KL28-08	11.5	14.5	0.0063		63	0.01	0.9	1470	322	14	2	0.01	2	0.7	0.5	26	0.01
KL28-08	14.5	17.5	0.004		40	0.01	0.8	116	119	17	3	0.01	3	0.7	1.4	24	0.01
KL28-08	17.5	20.5	0.0023		23	0.02	0.1	140	75	9	1	0.01	3	0.5	1.0	25	0.01
KL28-08	20.5	23.5	0.0045		45	0.04	0.6	139	132	11	3	0.01	1	0.9	3.8	21	0.01
KL28-08	23.5	26.5	0.004		40	0.01	0.1	78	93	5	2	0.01	1	0.9	1.4	18	0.01
KL28-08	26.5	29.5	0.0034		34	0.03	0.7	174	242	10	4	0.01	1	1.1	1.5	18	0.01
KL28-08	29.5	32.5	0.004		40	0.03	0.6	93	264	8	3	0.01	1	1.8	1.7	18	0.01
KL28-08	32.5	35.5	0.0073		73	0.01	4.8	6500	5100	14	10	1	1	5	1.0	28	0.01
KL28-08	35.5	38.5	0.005		50	0.09	10.3	13300	9100	40	6	25	1	8.3	3.5	23	0.01
KL28-08	38.5	41.5	0.0044		44	0.01	0.6	326	298	20	12	2	2	1.3	2.6	26	0.01
KL28-08	41.5	44.5	0.0024		24	0.21	1.6	187	610	45	11	1	1	2.1	3.1	22	0.01
KL28-08	44.5	47.5	0.0046		46	0.12	0.7	118	85	53	13	4	1	1.2	3.4	26	0.01
KL28-08	47.5	50.5	0.004		40	0.04	5.3	1170	1850	16	33	18	1	1.3	22.5	23	0.01
KL28-08	50.5	53.5	0.0037		37	0.03	4	1490	3320	24	26	10	1	1.8	40.5	36	0.01
KL28-08	53.5	56.5	0.0145		145	0.2	17.5	11500	11400	34	50	70	3	3.4	210.0	27	0.01
KL28-08	56.5	59.5	0.0179		179	0.07	29.5	8600	6000	24	20	172	1	4.5	115.0	35	0.01
KL28-08	59.5	62.5	0.0079		79	0.01	8.4	1690	5050	41	12	52	2	1.8	70.0	36	0.01
KL28-08	62.5	65.5	0.083		830	0.07	96	62800	16600	94	10	2450	4	8.3	825.0	62	0.01
KL28-08	65.5	68.5	0.0184		184	0.05	4.8	6100	770	22	18	350	1	1.6	43.0	23	0.01
KL28-08	68.5	71.5	0.0054		54	0.08	5.6	3360	2060	18	10	50	1	2.4	9.0	23	0.01
KL28-08	71.5	74.5	0.0016		16	0.11	0.6	216	344	25	6	0.01	1	1.9	1.8	17	0.01
KL28-08	74.5	77.5	0.0038		38	0.07	0.1	149	163	13	3	0.01	1	0.7	1.3	19	0.01
KL28-08	77.5	80.5	0.0018		18	0.05	0.5	292	580	19	5	1	2	1.1	2.4	21	0.01
KL28-08	80.5	83.5	0.0013		13	0.07	0.5	131	238	24	3	1	1	1.1	2.3	20	0.01
KL28-08	83.5	86.5	0.003		30	0.12	0.6	287	450	25	3	1	1	1.3	2.3	28	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL28-08	86.5	89.5	0.0015		15	0.01	0.1	228	312	13	7	0.01	1	0.8	1.5	18	0.01
KL28-08	89.5	92.5	0.0022		22	0.05	0.9	480	490	45	1	1	1	1.3	3.2	28	0.01
KL28-08	92.5	95.5	0.0014		14	0.04	0.5	227	330	15	4	0.01	1	0.9	2.5	28	0.01
KL28-08	95.5	98.5	0.0017		17	0.07	0.6	520	292	12	3	4	1	0.8	1.8	18	0.01
KL28-08	98.5	101.5	0.0027		27	0.04	0.1	71	158	9	7	0.01	1	0.6	1.1	26	0.01
KL28-08	101.5	104.5	0.0018		18	0.08	0.1	335	119	12	3	0.01	1	0.5	1.6	27	0.01
KL28-08	104.5	107.5	0.0033		33	0.01	0.1	122	225	24	5	0.01	1	0.3	4.6	25	0.01
KL28-08	107.5	110.5	0.0008		8	0.01	0.1	113	120	9	4	0.01	2	0.3	2.0	10	0.01
KL28-08	110.5	113.5	0.0028		28	0.01	0.7	177	102	15	2	5	1	0.6	4.3	22	0.01
KL28-08	113.5	116.5	0.0052		52	0.04	0.8	121	45	18	5	7	1	1.1	4.4	85	0.01
KL28-08	116.5	119.5	0.0048		48	0.04	0.6	90	41	28	1	5	3	1.5	6.8	78	0.01
KL28-08	119.5	122	0.0053		53	0.03	0.1	69	31	18	2	1	3	0.8	7.6	131	0.01
KL28-08	122	125.1	0.0025		25	0.04	0.1	60	29	13	4	3	4	0.5	7.6	102	0.01
KL28-08	125.1	127.8	0.0101		101	0.03	0.1	82	40	20	3	2	9	0.5	6.6	62	0.01
KL28-08	127.8	130.9	0.0154		154	0.03	0.6	112	77	20	3	3	11	0.4	6.6	54	0.01
KL28-08	130.9	132.4	0.431		4310	0.06	14	1150	384	30	8	8	7	1.3	19.8	90	0.01
KL28-08	132.4	134	1.06		10600	0.32	45	6800	2500	110	26	150	7	6.2	176.0	67	0.01
KL28-08	134	137.1	0.165		1650	0.3	25	1330	12400	73	8	78	6	5.8	12.0	28	0.01
KL28-08	137.1	140.2	0.321		3210	0.14	8	151	2360	6	10	19	2	1.8	9.5	93	0.01
KL28-08	140.2	143.2	0.0165		165	0.16	1.5	174	470	18	3	24	1	2.3	3.1	33	0.01
KL28-08	143.2	145.3	0.024		240	0.06	1.6	156	231	25	26	38	2	2.8	6.3	25	0.01
KL28-08	145.3	147	0.017		170	0.05	1.3	128	180	15	30	12	1	2.4	2.8	35	0.01
KL28-08	147	149.5	0.36		3600	0.25	4	120	273	8	24	14	2	1.3	9.3	63	0.01
KL28-08	149.5	152.5	0.415		4150	0.25	4	154	282	12	26	8	2	1.5	9.8	90	0.01
KL28-08	152.5	155.5	2.58		25800	0.36	16.5	312	850	30	24	8	5	1.6	15.0	145	0.01
KL28-08	155.5	158.3	1.19		11900	0.29	9.2	149	450	24	8	3	1	0.8	9.5	138	0.01
KL28-08	158.3	161.4	0.204		2040	0.1	2.2	180	155	15	62	3	1	2.8	5.6	82	0.01
KL28-08	161.4	164.4	0.048		480	0.07	1.7	460	178	46	90	40	1	3.8	4.6	46	0.01
KL28-08	164.4	167.4	0.053		530	0.09	1.4	350	227	16	32	6	2	1.7	5.5	78	0.01
KL28-08	167.4	170.4	0.22		2200	0.48	6.8	420	800	43	156	30	3	4.5	15.0	68	0.01
KL28-08	170.4	173.4	0.0184		184	0.08	2.2	359	182	17	107	10	2	2.2	5.0	108	0.01
KL28-08	173.4	176.5	0.0155		155	0.04	2.6	248	150	15	34	14	1	3.7	3.7	55	0.01
KL28-08	176.5	179.5	0.0213		213	0.06	1.9	114	158	18	180	12	1	3	4.4	73	0.01
KL28-08	179.5	182.5	0.0169		169	0.08	1.8	61	120	14	69	7	1	0.9	3.1	40	0.01
KL28-08	182.5	185.5	0.0197		197	0.06	2.5	67	288	11	460	14	1	1.3	5.5	20	0.01
KL28-08	185.5	188.5	0.0152		152	0.05	1.1	66	134	1	430	3	1	1.4	4.2	23	0.01
KL28-08	188.5	191.5	0.0311		311	0.07	2.3	470	414	27	106	4	2	2.2	5.9	30	0.01
KL28-08	191.5	193.4	0.318		3180	1.72	71	29400	7400	250	260	298	50	10.4	126.0	45	0.01
KL28-08	193.4	196.2	0.345		3450	0.76	224	98400	75400	140	500	560	8	43.5	463.0	78	0.01
KL28-08	196.2	198.4	0.055		550	0.18	67	12100	16600	21	56	140	2	6.8	72.5	33	0.01
KL28-08	198.4	200.4	0.0101		101	0.06	4.4	1120	2760	12	88	7	1	1.5	7.6	32	0.01
KL28-08	200.4	202.8	0.015		150	0.07	7.4	4830	8000	29	40	10	1	5.5	21.0	26	0.01
KL28-08	202.8	205.9	0.0078		78	0.03	4.6	1700	3770	25	34	6	1	3	13.8	18	0.01
KL28-08	205.9	207.7	0.0141		141	0.06	6	3760	3810	33	100	12	1	2.8	8.0	15	0.01
KL28-08	207.7	210.2	0.0088		88	0.04	14	1540	4160	16	25	29	1	3	12.3	23	0.01
KL28-08	210.2	212.6	0.0098		98	0.04	5	1450	1910	34	32	14	1	1.2	6.1	17	0.01
KL28-08	212.6	215.5	0.0109		109	0.04	2.9	1440	2050	7	39	2	1	1.8	8.8	18	0.01
KL28-08	215.5	218.5	0.0214		214	0.05	6.8	7300	6100	31	80	4	1	6.5	16.0	30	0.1
KL28-08	218.5	221.5	0.019		190	0.04	2.4	1280	2340	30	65	4	1	3.7	6.8	19	0.01
KL28-08	221.5	224.5	0.0135		135	0.02	2.5	610	2630	20	34	4	1	2.5	4.8	20	0.01
KL28-08	224.5	227.5	0.0108		108	0.04	3.7	2740	4010	13	49	2	1	4.9	4.5	23	0.01
KL28-08	227.5	230	0.054		540	0.04	6.8	2600	14600	40	38	5	1	11.8	38.0	23	0.01
KL28-08	230	231.5	0.083		830	0.1	32	9600	28000	50	53	50	1	27.3	45.5	23	0.01
KL28-08	231.5	234	0.0262		262	0.05	3.2	1370	3240	24	61	13	2	2.6	10.0	26	0.01
KL28-08	234	236.7	0.0165		165	0.02	4	640	6700	18	42	5	2	7.8	11.0	33	0.01
KL28-08	236.7	239.5	0.0169		169	0.02	3.3	1380	3900	32	25	8	2	5.8	4.0	26	0.01
KL28-08	239.5	242.3	0.0324		324	0.04	7.3	3580	6800	37	20	17	2	5.2	15.7	34	0.01
KL28-08	242.3	245.5	0.0179		179	0.04	5.2	2650	4360	20	14	15	2	2.6	9.0	33	0.01
KL28-08	245.5	247.8	0.0338		338	0.05	4.8	2370	3350	68	20	14	3	11.4	8.6	52	0.01
KL28-08	247.8	250.5	0.052		520	0.04	4.8	3060	2720	22	24	34	2	3.5	9.0	34	0.01
KL28-08	250.5	253.6	0.115		1150	0.14	14	6100	5600	51	17	147	4	4.6	19.1	39	0.01
KL28-08	253.6	256.7	0.085		850	0.09	29	4700	14400	36	25	210	6	13.3	17.8	26	0.01
KL28-08	256.7	259.8	0.0203		203	0.04	14	1810	3260	12	17	52	3	2.5	7.3	21	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL28-08	259.8	262.9	0.0124	124	0.03	4.2	3040	7200	6	30	7	1	2.8	5.0	14	0.01
KL28-08	262.9	266	0.0125	125	0.02	3.7	6200	4100	3	29	6	1	1.8	5.3	10	0.01
KL28-08	266	269.1	0.0163	163	0.03	2.8	3440	6200	8	17	6	1	3.4	15.8	16	0.01
KL28-08	269.1	271.9	0.128	1280	0.12	4.6	3170	5430	15	100	7	4	2.1	15.0	26	0.01
KL28-08	271.9	274.1	0.27	2700	0.9	39	18900	26000	26	20	285	7	9.2	375.0	30	0.01
KL28-08	274.1	276.6	0.955	9550	3.67	104	44000	88700	27	185	910	18	3.7	630.0	25	0.01
KL28-08	276.6	278.5	0.56	5600	1.39	35	39600	27300	17	123	177	13	19.2	229.0	26	0.01
KL28-08	278.5	281.5	0.079	790	0.25	14.2	18700	18000	21	46	110	8	17.2	155.0	35	0.1
KL28-08	281.5	284.5	0.078	780	0.46	10	18900	8200	20	128	54	15	22	84.0	31	0.11
KL28-08	284.5	287.5	0.059	590	0.73	7.4	25300	640	10	13	115	26	13.4	110.0	20	0.01
KL28-08	287.5	290.5	0.27	2700	0.64	6.1	20300	1500	1	8	45	21	13.5	46.8	24	0.01
KL28-08	290.5	293.5	0.058	580	0.13	0.7	13400	29	0.01	2	4	15	0.6	14.5	16	0.01
KL28-08	293.5	296.5	0.032	320	0.08	0.8	2580	327	2	2	7	7	0.5	6.5	14	0.01
KL28-08	296.5	299.5	0.041	410	0.09	1	2980	221	6	8	14	5	1.2	6.0	10	0.01
KL28-08	299.5	302.7	0.86	8600	1.7	1.9	4200	42	4	20	6	33	1.5	29.3	20	0.01
KL28-08	302.7	305.5	0.78	7800	0.92	1.6	1450	55	11	94	1	31	0.2	16.8	19	0.01
KL28-08	305.5	308.5	0.67	6700	0.72	1.5	5500	27	1	470	3	25	0.4	16.8	16	0.01
KL28-08	308.5	311.5	0.8	8000	1.19	1.3	348	28	1	35	0.01	23	0.3	16.3	18	0.01
KL28-08	311.5	314.5	0.77	7700	1	1.2	940	31	5	84	0.01	23	0.01	19.3	31	0.01
KL28-08	314.5	317.5	0.51	5100	0.63	0.7	232	35	1	840	0.01	16	0.01	12.3	20	0.01
KL28-08	317.5	320.5	0.056	560	0.13	0.1	122	25	0.01	230	0.01	5	0.01	10.0	13	0.01
KL28-08	320.5	323.5	0.191	1910	0.49	0.6	341	91	1	32	9	10	0.01	7.8	19	0.01
KL28-08	323.5	326.5	0.126	1260	0.2	0.1	158	23	2	75	1	8	0.01	4.0	13	0.01
KL28-08	326.5	329.5	0.255	2550	0.37	1	550	64	2	41	2	15	0.4	6.3	14	0.01
KL28-08	329.5	332.5	0.194	1940	0.19	4.1	5100	5900	22	224	2	9	4.6	13.3	33	0.1
KL28-08	332.5	335.5	0.157	1570	0.41	1	293	185	26	212	1	10	0.6	4.5	31	0.01
KL28-08	335.5	338.5	0.05	500	0.3	0.6	265	142	14	40	1	10	0.2	2.3	22	0.01
KL28-08	338.5	341.5	0.62	6200	0.86	1.9	910	101	7	85	3	43	0.6	19.0	14	0.01
KL28-08	341.5	344.5	1	10000	1.44	2.2	1190	44	1	270	2	56	0.01	23.2	33	0.01
KL28-08	344.5	347.5	0.64	6400	1.06	1.6	710	82	0.01	70	3	39	0.2	22.5	14	0.01
KL28-08	347.5	350.5	0.3	3000	0.74	1.3	950	860	9	136	7	22	0.6	12.3	13	0.01
KL28-08	350.5	353.5	0.151	1510	0.3	0.1	214	42	2	59	1	14	0.2	4.4	16	0.01
KL28-08	353.5	356.5	0.22	2200	0.68	0.1	205	40	4	47	0.01	38	0.01	15.8	17	0.01
KL28-08	356.5	359.5	2.34	23400	3.33	7.5	1380	274	6	20	1	49	0.01	32.5	21	0.01
KL28-08	359.5	362.5	0.58	5800	0.81	1.1	335	137	1	29	6	21	0.3	16.3	18	0.01
KL28-08	362.5	365.5	0.25	2500	0.49	1.3	168	57	1	51	3	14	0.01	11.0	14	0.01
KL28-08	365.5	368.5	0.28	2800	0.86	1	105	24	2	1380	2	12	0.01	11.5	23	0.01
KL28-08	368.5	371.5	0.74	7400	2.06	1.6	104	25	15	750	0.01	26	0.01	9.8	38	0.01
KL28-08	371.5	374.5	0.85	8500	1.81	2.2	125	35	6	1680	1	15	0.01	10.0	20	0.01
KL28-08	374.5	377.5	1.02	10200	2.15	3.4	440	203	17	1340	2	28	0.01	13.8	41	0.01
KL28-08	377.5	380.5	3.32	33200	5.19	8	880	54	3	242	0.01	38	0.01	17.5	34	0.01
KL28-08	380.5	383.5	3.28	32800	3.8	5.5	710	262	1	231	1	56	0.01	23.5	29	0.01
KL28-08	383.5	386.5	2.35	23500	1.84	4.2	420	38	2	11	0.01	67	0.01	30.0	15	0.01
KL28-08	386.5	389.5	1.46	14600	0.99	1.8	510	155	0.01	1290	0.01	53	0.01	13.3	20	0.01
KL28-08	389.5	392.5	1.12	11200	0.8	1.1	266	58	0.01	71	1	43	0.01	11.0	13	0.01
KL28-08	392.5	395.5	3.05	30500	2.89	3.5	329	34	0.01	1740	0.01	71	0.01	27.5	11	0.01
KL28-08	395.5	398.5	1.55	15500	1.09	8	2650	670	5	121	0.01	53	0.9	13.5	15	0.01
KL28-08	398.5	401.5	1.08	10800	0.95	4.8	232	130	4	306	3	39	0.4	17.5	17	0.01
KL28-08	401.5	404.5	0.315	3150	0.69	1.5	440	202	12	20	1	65	0.4	20.3	29	0.01
KL28-08	404.5	407.5	0.56	5600	0.6	2.5	5200	600	20	27	14	61	1.4	16.8	14	0.01
KL28-08	407.5	410.5	1.7	17000	1.27	2.1	183	18	0.01	89	0.01	40	0.01	10.0	11	0.01
KL28-08	410.5	413.5	1.6	16000	1.19	2.9	159	21	3	180	2	71	0.01	31.0	12	0.01
KL28-08	413.5	415	3.14	31400	1.9	10	321	27	7	48	0.01	29	0.7	10.0	23	0.1
KL28-08	415	417.7	3.94	39400	2.35	5.9	220	14	0.01	13	0.01	41	0.01	11.3	16	0.01
KL28-08	417.7	419.5	1.3	13000	0.82	2.1	248	19	3	80	0.01	28	0.01	12.0	13	0.01
KL28-08	419.5	422.9	0.6	6000	0.28	1.2	221	34	21	152	7	23	0.2	15.8	34	0.01
KL28-08	422.9	425.5	0.56	5600	0.32	1	147	9	3	120	2	74	0.3	5.8	12	0.01
KL28-08	425.5	428.5	0.77	7700	0.89	2.2	164	32	2	24	2	54	0.01	6.0	6	0.01
KL28-08	428.5	431.5	0.375	3750	0.4	0.8	76	11	2	35	2	103	0.01	16.0	14	0.01
KL28-08	431.5	434.5	0.215	2150	0.19	0.1	89	11	0.01	28	1	91	0.01	17.3	10	0.01
KL28-08	434.5	437.5	0.52	5200	0.47	1.3	81	12	1	60	2	82	0.01	20.9	21	0.01
KL28-08	437.5	440.5	0.28	2800	0.24	0.7	116	17	0.01	57	0.01	56	0.01	14.8	19	0.01
KL28-08	440.5	443.5	0.29	2900	0.36	1.1	113	15	0.01	34	1	73	0.01	12.0	12	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL28-08	443.5	446.5	0.38	3800	0.39	0.8	153	29	0.01	30	1	57	0.01	16.5	24	0.01
KL28-08	446.5	449.5	0.52	5200	0.51	1.3	161	18	0.01	241	2	51	0.01	8.5	17	0.01
KL28-08	449.5	452	2.26	22600	1.27	14.3	450	144	2	720	1	52	0.6	28.5	22	0.01
KL28-08	452	453.7	1.81	18100	1.05	5.4	6100	42	0.01	145	0.01	34	0.01	12.0	14	0.01
KL28-08	453.7	455.5	0.91	9100	0.73	1.8	159	17	0.01	36	2	38	0.2	11.8	18	0.01
KL28-08	455.5	458.5	2.21	22100	0.45	3.6	141	20	5	110	2	54	0.01	39.5	25	0.01
KL28-08	458.5	461.5	1.18	11800	1.19	1.9	95	21	0.01	114	2	25	0.01	13.5	36	0.01
KL28-08	461.5	462.5	1.6	16000	3.46	2.5	50	9	1	218	5	10	0.01	15.2	114	0.01
KL28-08	462.5	464.5	0.49	4900	0.12	1.3	40	10	3	181	1	8	0.01	6.0	67	0.01
KL28-08	464.5	466.3	1.47	14700	0.65	3.8	125	18	1	219	4	34	0.01	23.5	55	0.01
KL28-08	466.3	468	0.441	4410	0.12	1.8	141	13	12	590	2	17	0.01	9.8	39	0.01
KL28-08	468	470.5	0.66	6600	0.21	2.3	126	17	6	530	0.01	19	0.01	7.3	42	0.01
KL28-08	470.5	473.5	0.82	8200	0.25	2.7	232	15	5	310	1	13	0.01	6.8	50	0.01
KL28-08	473.5	476.5	0.61	6100	0.25	1.8	118	14	2	290	1	14	0.01	11.3	160	0.01
KL28-08	476.5	479.5	0.67	6700	0.35	1.7	178	22	4	190	5	18	0.5	8.3	74	0.01
KL28-08	479.5	482.5	0.52	5200	0.21	1.2	102	10	0.01	199	0.01	23	0.2	6.5	66	0.01
KL28-08	482.5	485.5	0.67	6700	0.33	1.8	248	196	0.01	236	0.01	16	0.01	7.3	83	0.01
KL28-08	485.5	488.5	0.97	9700	0.7	1.9	159	15	1	184	0.01	15	0.01	5.4	86	0.01
KL28-08	488.5	491.5	0.483	4830	0.24	1.8	65	11	0.01	374	0.01	11	0.01	5.0	77	0.01
KL28-08	491.5	494.5	0.98	9800	0.66	2.1	48	10	1	187	1	16	0.01	6.0	75	0.01
KL28-08	494.5	497.5	0.95	9500	0.44	2.5	64	10	2	729	0.01	20	0.2	8.8	81	0.01
KL28-08	497.5	500.5	0.62	6200	0.3	1.4	72	7	0.01	290	0.01	15	0.01	5.5	77	0.01
KL28-08	500.5	503.5	0.73	7300	0.5	1.3	77	9	0.01	168	0.01	17	0.2	4.3	86	0.01
KL28-08	503.5	506.5	1.34	13400	0.81	2.1	235	68	1	259	4	15	0.2	6.5	63	0.01
KL28-08	506.5	509.5	1.67	16700	0.63	3.2	225	69	41	751	1	18	2.3	8.0	57	0.01
KL28-08	509.5	512.5	1.27	12700	0.64	2.5	107	40	0.01	73	1	16	0.01	8.0	83	0.01
KL28-08	512.5	515.5	1.26	12600	0.68	2.5	89	11	0.01	121	0.01	20	0.01	3.5	71	0.01
KL28-08	515.5	518.5	0.97	9700	0.43	2.2	96	8	0.01	91	0.01	18	0.01	5.8	58	0.01
KL28-08	518.5	521.5	0.71	7100	0.57	1.5	64	11	0.01	200	0.01	10	0.01	7.4	53	0.01
KL28-08	521.5	524.5	0.58	5800	0.42	1.7	56	11	2	158	1	10	0.2	5.5	58	0.01
KL28-08	524.5	527.5	0.7	7000	0.45	2.8	73	165	1	261	12	13	0.2	8.0	61	0.01
KL28-08	527.5	530.5	1.05	10500	0.54	2.7	74	18	2	215	1	19	1.1	8.8	59	0.01
KL28-08	530.5	533.5	1.03	10300	0.5	2.9	87	53	18	99	1	16	1.6	6.0	64	0.01
KL28-08	533.5	535	0.36	3600	0.07	1.4	74	41	38	156	1	11	2	7.3	50	0.01
KL28-08	535	536.5	0.33	3300	0.07	1.1	46	24	22	162	1	21	0.6	7.0	63	0.01
KL28-08	536.5	539.5	0.33	3300	0.07	1.5	137	83	37	127	1	15	2.3	7.0	61	0.01
KL28-08	539.5	542.5	0.33	3300	0.07	1.2	226	56	23	124	4	17	2	7.5	54	0.01
KL28-08	542.5	545.5	0.427	4270	0.26	2.2	378	146	2	96	8	21	0.2	10.3	57	0.01
KL28-08	545.5	548.5	0.345	3450	0.2	1.6	136	45	10	59	3	15	0.3	6.7	52	0.01
KL28-08	548.5	551.5	0.085	850	0.07	100	61500	19400	100	18	2970	5	8.8	775.0	62	0.01
KL28-08	551.5	554.5	0.3	3000	0.07	1.2	198	56	2	32	6	9	0.3	9.3	58	0.01
KL28-08	554.5	557.5	0.27	2700	0.12	1	78	129	2	30	2	13	0.3	9.0	72	0.01
KL28-08	557.5	560.5	0.89	8900	0.3	6.7	1400	500	6	28	9	16	0.5	9.3	71	0.01
KL28-08	560.5	563.5	0.8	8000	0.31	4.5	630	315	2	54	3	18	0.3	8.0	63	0.01
KL28-08	563.5	566.5	0.57	5700	0.23	1.7	91	28	2	88	1	22	0.2	8.8	70	0.01
KL28-08	566.5	569.5	0.38	3800	0.23	1.4	71	18	1	50	1	13	0.01	7.3	61	0.01
KL28-08	569.5	571.6	0.404	4040	0.24	1.1	78	25	2	68	1	14	0.01	7.0	68	0.01
KL28-08	571.6	574.7	0.27	2700	0.13	1.3	60	20	2	55	1	13	0.2	6.0	66	0.01
KL28-08	574.7	577.8	0.39	3900	0.23	1.8	84	70	2	43	1	21	0.2	7.8	51	0.01
KL28-08	577.8	580.9	0.32	3200	0.27	2.1	304	121	1	85	18	20	0.01	11.0	69	0.01
KL28-08	580.9	582.7	0.37	3700	0.23	1.2	67	27	2	64	0.01	12	0.01	6.8	73	0.01
KL28-08	582.7	584	0.24	2400	0.22	1.3	72	31	15	21	2	10	0.01	9.3	69	0.01
KL28-08	584	587.1	0.39	3900	0.21	1.5	96	125	6	62	3	12	0.2	9.3	73	0.01
KL28-08	587.1	590.3	0.492	4920	0.24	1.3	59	22	5	85	0.01	10	0.01	6.0	49	0.01
KL28-08	590.3	593.4	0.32	3200	0.23	1.1	47	18	3	218	1	8	0.01	5.1	48	0.01
KL28-08	593.4	596.5	0.487	4870	0.23	1.4	55	16	1	91	0.01	9	0.01	4.2	54	0.01
KL28-08	596.5	598.1	1	10000	0.45	2	83	10	0.01	46	0.01	17	0.01	7.3	61	0.01
KL28-08	598.1	600.4	1.38	13800	0.67	2.4	90	12	0.01	111	0.01	21	0.01	9.0	73	0.01
KL28-08	600.4	602.5	1.95	19500	0.99	3.8	92	28	1	82	3	6	0.01	10.5	143	0.01
KL28-08	602.5	605.5	1.29	12900	0.55	2.6	64	19	0.01	21	1	7	0.01	8.0	133	0.01
KL28-08	605.5	608.5	0.75	7500	0.43	1.3	21	10	0.01	20	1	9	0.01	5.7	185	0.01
KL28-08	608.5	611.5	0.95	9500	0.68	1.6	28	11	0.01	45	2	7	0.01	6.0	121	0.01
KL28-08	611.5	614.5	1.3	13000	0.26	2.3	392	120	4	15	1	7	0.01	6.5	152	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL28-08	614.5	617.5	1.33	13300	0.46	3.6	312	100	45	16	2	6	0.3	8.0	84	0.01
KL28-08	617.5	620.5	1.24	12400	0.57	2.5	183	61	13	20	3	5	0.01	7.8	170	0.01
KL28-08	620.5	623.5	1.38	13800	1.09	2.9	23	9	0.01	21	1	10	0.01	6.5	131	0.01
KL28-08	623.5	626.5	1.32	13200	0.55	2.7	70	30	1	28	1	10	0.01	6.5	110	0.01
KL28-08	626.5	629.5	0.8	8000	0.33	2.4	67	23	1	38	0.01	11	0.01	4.8	115	0.01
KL28-08	629.5	632.5	0.59	5900	0.27	2	35	17	0.01	45	0.01	7	0.01	4.8	120	0.01
KL28-08	632.5	635.5	0.74	7400	0.23	1.6	54	32	3	23	1	8	0.01	4.0	125	0.01
KL28-08	635.5	638.5	1.12	11200	0.44	3	2330	298	1680	14	5	6	65	5.5	89	0.27
KL28-08	638.5	641.5	0.85	8500	0.71	2.1	66	15	3	185	1	7	0.2	5.0	143	0.01
KL28-08	641.5	644.4	0.45	4500	0.17	1.2	44	11	1	43	0.01	2	0.01	4.3	120	0.01
KL28-08	644.4	647.5	0.22	2200	0.09	1	51	16	2	38	0.01	2	0.01	1.8	177	0.01
KL28-08	647.5	650.5	0.38	3800	0.15	1.4	32	12	7	7	0.01	4	0.01	3.5	102	0.01
KL28-08	650.5	653.5	0.23	2300	0.18	1.4	37	15	18	26	1	9	0.2	10.4	73	0.01
KL28-08	653.5	656.5	0.36	3600	0.34	1.7	36	10	0.01	50	0.01	10	0.5	1.8	135	0.01
KL28-08	656.5	659.5	0.64	6400	0.35	2.3	64	19	3	20	0.01	7	0.2	5.3	168	0.01
KL28-08	659.5	662.5	0.49	4900	0.33	1.7	76	141	5	10	0.01	6	0.3	5.8	79	0.01
KL28-08	662.5	665.5	0.61	6100	0.34	1.8	39	12	0.01	21	0.01	6	0.01	4.0	195	0.01
KL28-08	665.5	668.5	0.64	6400	0.47	1.8	21	11	0.01	13	0.01	6	0.01	4.3	253	0.01
KL28-08	668.5	671.5	0.38	3800	0.27	1.1	31	6	0.01	22	1	7	0.01	3.3	189	0.01
KL28-08	671.5	674.5	0.489	4890	0.26	1.8	33	13	0.01	28	1	8	0.01	4.5	165	0.01
KL28-08	674.5	677.5	0.465	4650	0.31	1.5	28	19	0.01	40	0.01	7	0.01	3.5	101	0.01
KL28-08	677.5	680.5	0.435	4350	0.29	1.6	39	48	1	14	0.01	7	0.01	3.5	78	0.01
KL28-08	680.5	683.5	0.42	4200	0.21	1.4	77	24	0.01	14	0.01	5	0.01	2.9	107	0.01
KL28-08	683.5	686.5	0.418	4180	0.23	1.6	49	20	0.01	42	0.01	5	0.01	3.5	154	0.01
KL28-08	686.5	689.5	0.31	3100	0.26	1.7	33	7	0.01	27	0.01	4	0.01	1.5	61	0.01
KL28-08	689.5	692.5	0.26	2600	0.13	1.2	38	10	0.01	38	0.01	4	0.01	1.3	82	0.01
KL28-08	692.5	695.5	0.35	3500	0.13	1.4	106	25	24	12	0.01	5	0.5	2.8	80	0.01
KL28-08	695.5	698.5	0.65	6500	0.29	1.3	16	10	1	22	0.01	4	0.01	5.3	82	0.01
KL28-08	698.5	701.5	0.437	4370	0.21	1.2	30	13	2	17	0.01	6	0.2	2.8	145	0.01
KL28-08	701.5	704.5	0.56	5600	0.21	1.1	40	9	1	18	0.01	5	0.01	3.3	111	0.01
KL28-08	704.5	707.5	0.67	6700	0.27	1.7	72	14	150	50	0.01	7	1	3.8	174	0.01
KL28-08	707.5	710.5	0.444	4440	0.2	1.1	53	19	16	26	0.01	5	0.3	3.8	81	0.01
KL28-08	710.5	713.5	0.43	4300	0.17	1.3	27	8	1	18	0.01	5	0.2	1.8	88	0.01
KL28-08	713.5	716.5	0.38	3800	0.19	1.5	32	8	0.01	23	0.01	6	0.2	4.1	170	0.01
KL28-08	716.5	719.5	0.27	2700	0.14	1.2	28	8	1	14	0.01	5	0.2	2.5	160	0.01
KL28-08	719.5	722.5	0.68	6800	0.37	1.8	38	12	1	22	0.01	6	0.3	5.0	142	0.01
KL28-08	722.5	725.5	0.23	2300	0.09	0.6	29	9	0.01	33	0.01	5	0.2	4.0	149	0.01
KL28-08	725.5	728.5	0.325	3250	0.14	1.1	38	11	1	15	1	7	0.01	2.8	105	0.01
KL28-08	728.5	731.5	0.24	2400	0.16	0.7	26	12	0.01	54	0.01	6	0.2	3.3	143	0.01
KL28-08	731.5	734.5	0.37	3700	0.2	1.3	34	11	0.01	36	0.01	14	0.01	4.6	181	0.01
KL28-08	734.5	737.5	0.91	9100	0.35	2.1	38	10	1	23	1	24	0.2	5.3	135	0.01
KL28-08	737.5	740.5	0.69	6900	0.29	1.1	39	12	3	22	0.01	23	0.01	4.0	130	0.01
KL28-08	740.5	743.5	0.27	2700	0.12	0.8	48	81	16	40	0.01	12	0.9	2.5	105	0.01
KL28-08	743.5	746.5	0.464	4640	0.32	1	45	54	3	13	0.01	9	0.01	3.0	137	0.01
KL28-08	746.5	749.5	0.64	6400	0.32	1.4	36	14	0.01	26	0.01	11	0.2	4.3	137	0.01
KL28-08	749.5	752.5	0.61	6100	0.37	1.5	82	37	230	27	0.01	7	14	3.8	136	0.26
KL28-08	752.5	755.5	0.68	6800	0.31	4.7	2260	2230	650	12	0.01	9	105	3.8	195	2.16
KL28-08	755.5	758.5	0.78	7800	0.33	1.8	51	20	5	80	0.01	11	0.6	5.0	148	0.01
KL28-08	758.5	761.5	0.66	6600	0.38	1.9	38	20	8	12	0.01	10	0.5	5.3	147	0.01
KL28-08	761.5	764.5	0.56	5600	0.28	1.5	33	17	2	16	0.01	8	0.3	5.0	99	0.01
KL28-08	764.5	767.5	0.44	4400	0.21	1.4	29	12	7	24	0.01	9	0.3	3.8	82	0.01
KL28-08	767.5	770.5	0.245	2450	0.06	0.1	32	9	0.01	20	0.01	7	0.01	3.1	76	0.01
KL28-08	770.5	773.5	0.58	5800	0.2	1.2	25	6	2	22	0.01	4	0.01	4.3	98	0.01
KL28-08	773.5	776.5	0.417	4170	0.2	0.8	27	6	1	12	0.01	7	0.01	3.3	102	0.01
KL28-08	776.5	779.5	0.3	3000	0.16	0.6	26	12	2	19	0.01	6	0.01	2.8	140	0.01
KL28-08	779.5	782.5	0.507	5070	0.34	0.9	31	7	2	26	0.01	8	0.2	4.8	115	0.01
KL28-08	782.5	785.5	0.395	3950	0.26	0.7	43	7	0.01	23	0.01	8	0.2	3.9	85	0.01
KL28-08	785.5	788.5	0.35	3500	0.18	0.9	44	6	1	16	0.01	9	0.01	3.5	102	0.01
KL28-08	788.5	791.5	0.493	4930	0.37	1.1	34	6	1	19	0.01	7	0.01	3.0	98	0.01
KL28-08	791.5	794.5	0.68	6800	0.24	1.3	58	10	3	20	0.01	12	0.3	4.5	125	0.01
KL28-08	794.5	797.5	0.486	4860	0.25	1.1	43	8	1	23	0.01	13	0.01	4.5	131	0.01
KL28-08	797.5	800.5	0.56	5600	0.31	1.4	46	5	1	26	0.01	13	0.01	3.8	175	0.01
KL28-08	800.5	803.5	0.48	4800	0.22	0.8	33	5	1	17	0.01	10	0.01	4.2	115	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL28-08	803.5	806.5	0.34	3400	0.18	0.6	35	8	1	17	0.01	12	0.01	3.3	107	0.01
KL28-08	806.5	809.5	0.32	3200	0.14	0.7	41	9	1	21	0.01	13	0.01	3.7	105	0.01
KL28-08	809.5	812.5	0.73	7300	0.37	1.1	46	7	3	24	0.01	14	0.01	4.5	130	0.01
KL28-08	812.5	815.5	0.21	2100	0.08	0.1	50	5	0.01	19	0.01	10	0.01	2.7	132	0.01
KL28-08	815.5	818.5	0.28	2800	0.14	0.1	36	33	12	39	1	10	0.3	1.9	125	0.01
KL28-08	818.5	821.5	0.28	2800	0.16	0.6	242	112	280	21	0.01	9	6.8	2.8	153	0.01
KL28-08	821.5	824.5	0.56	5600	0.28	1	53	117	10	20	0.01	14	0.5	4.8	111	0.01
KL28-08	824.5	827.5	0.26	2600	0.1	0.5	34	10	1	27	0.01	9	0.01	3.2	102	0.01
KL28-08	827.5	830.5	0.28	2800	0.08	0.5	30	6	1	34	0.01	8	0.01	3.0	109	0.01
KL28-08	830.5	833.5	0.28	2800	0.12	0.1	33	5	1	15	0.01	9	0.2	3.4	111	0.01
KL28-08	833.5	836.5	0.179	1790	0.05	2.8	299	4000	40	16	0.01	6	22	2.0	100	0.11
KL28-08	836.5	839.5	0.27	2700	0.08	0.1	38	19	1	9	0.01	8	0.01	2.8	123	0.01
KL28-08	839.5	842.5	0.24	2400	0.08	0.1	23	11	3	8	0.01	6	0.01	2.6	125	0.01
KL28-08	842.5	845.5	0.29	2900	0.09	0.1	34	47	11	12	0.01	8	0.3	2.9	119	0.01
KL28-08	845.5	848.5	0.184	1840	0.06	0.1	24	13	2	26	0.01	9	0.01	2.1	212	0.01
KL28-08	848.5	851.5	0.389	3890	0.16	0.9	28	13	5	30	0.01	9	0.4	3.6	146	0.01
KL28-08	851.5	854.5	0.394	3940	0.33	5.2	142	740	380	12	0.01	9	36	2.9	213	0.12
KL28-08	854.5	857.5	0.55	5500	0.3	1.5	51	12	5	16	1	8	0.2	3.8	125	0.01
KL28-08	857.5	860.5	0.27	2700	0.17	0.6	36	30	5	19	0.01	8	3.5	2.6	94	0.01
KL28-08	860.5	863.5	0.26	2600	0.12	0.8	40	6	1	20	0.01	8	0.01	2.9	115	0.01
KL28-08	863.5	866.5	0.37	3700	0.18	1	30	10	3	27	0.01	11	0.4	2.7	76	0.01
KL28-08	866.5	869.5	0.26	2600	0.07	0.6	26	12	2	29	0.01	8	0.01	2.7	116	0.01
KL28-08	869.5	872.5	0.25	2500	0.08	0.7	35	8	2	26	0.01	8	0.01	3.0	91	0.01
KL28-08	872.5	875.5	0.164	1640	0.06	0.5	26	9	0.01	13	0.01	7	0.01	2.5	71	0.01
KL28-08	875.5	878.5	0.22	2200	0.07	0.6	33	5	0.01	22	0.01	11	0.01	3.4	100	0.01
KL28-08	878.5	881.5	0.199	1990	0.05	0.8	34	6	2	39	0.01	10	0.01	2.8	103	0.01
KL28-08	881.5	884.5	0.24	2400	0.06	0.6	29	5	1	23	0.01	8	0.3	3.3	83	0.01
KL28-08	884.5	887.5	0.22	2200	0.08	0.5	31	6	0.01	22	0.01	7	0.01	2.4	88	0.01
KL28-08	887.5	890.5	0.48	4800	0.14	1.1	35	6	2	18	0.01	7	0.01	3.6	90	0.01
KL28-08	890.5	893.5	0.43	4300	0.09	1.1	34	7	2	20	0.01	8	0.2	2.7	95	0.01
KL28-08	893.5	896.5	0.31	3100	0.13	1.2	40	6	1	22	1	8	0.01	3.8	121	0.01
KL28-08	896.5	899.5	0.38	3800	0.12	1	34	1	0.01	25	0.01	9	0.01	3.3	123	0.01
KL28-08	899.5	902.5	0.431	4310	0.18	0.9	51	6	0.01	26	0.01	10	0.01	4.4	76	0.01
KL28-08	902.5	905.5	0.44	4400	0.13	0.9	34	1	0.01	16	0.01	10	0.01	4.0	122	0.01
KL28-08	905.5	908.5	0.34	3400	0.11	1	29	5	0.01	24	0.01	11	0.01	3.5	97	0.01
KL28-08	908.5	911.5	0.26	2600	0.07	0.8	32	7	0.01	39	0.01	8	0.01	2.8	87	0.01
KL28-08	911.5	914.5	0.29	2900	0.11	1	42	5	2	12	1	8	0.01	3.7	111	0.01
KL28-08	914.5	917.5	0.38	3800	0.17	1.1	43	7	2	20	1	11	0.2	3.3	83	0.01
KL28-08	917.5	920.5	0.32	3200	0.15	1	39	5	2	16	0.01	14	0.01	3.8	91	0.01
KL28-08	920.5	923.5	0.25	2500	0.08	0.8	33	1	1	13	0.01	11	0.2	3.2	93	0.01
KL28-08	923.5	926.5	0.22	2200	0.07	0.6	42	8	0.01	13	0.01	7	0.01	3.1	87	0.01
KL28-08	926.5	929.5	0.26	2600	0.07	0.6	39	20	0.01	16	0.01	6	0.01	2.0	123	0.01
KL28-08	929.5	932.5	0.31	3100	0.76	0.9	37	26	1	20	1	7	0.2	2.2	141	0.01
KL28-08	932.5	935.5	0.41	4100	0.3	1.1	31	16	4	15	3	8	0.3	2.5	138	0.01
KL28-08	935.5	938.5	0.58	5800	0.33	1.7	48	6	0.01	12	4	12	0.01	5.0	204	0.01
KL28-08	938.5	941.5	0.45	4500	0.3	1.2	50	9	2	6	1	15	0.01	3.8	241	0.01
KL28-08	941.5	944.5	0.75	7500	0.51	1.8	36	7	3	7	2	16	0.01	5.9	196	0.01
KL28-08	944.5	947.5	0.3	3000	0.12	8.1	148	1510	130	35	2	10	36	2.3	87	0.73
KL28-08	947.5	950.5	0.32	3200	0.08	1.2	35	90	12	24	0.01	7	5.5	2.3	191	0.01
KL28-08	950.5	952.8	0.33	3300	0.08	3.4	64	213	33	26	0.01	6	16.8	1.7	97	0.34
KL28-08	952.8	955.8	0.38	3800	0.07	1.1	30	9	15	42	0.01	7	2.3	2.5	136	0.01
KL28-08	955.8	958.9	0.3	3000	0.06	0.6	23	8	8	31	0.01	12	0.2	2.7	135	0.01
KL28-08	958.9	962	0.29	2900	0.06	0.8	20	15	2	48	0.01	10	0.01	2.6	103	0.01
KL28-08	962	965.1	0.31	3100	0.05	0.6	21	7	0.01	35	0.01	11	0.01	2.1	130	0.01
KL28-08	965.1	968.2	0.36	3600	0.08	1	33	12	1	49	0.01	9	0.01	2.0	121	0.01
KL28-08	968.2	971.3	0.36	3600	0.09	1	33	8	1	32	0.01	9	0.01	2.7	106	0.01
KL28-08	971.3	974.4	0.28	2800	0.1	0.8	30	8	0.01	31	0.01	8	0.01	2.5	127	0.01
KL28-08	974.4	977.5	0.59	5900	0.22	1.8	36	10	2	28	1	8	0.01	3.3	130	0.01
KL28-08	977.5	980.5	0.376	3760	0.08	0.9	26	6	1	71	0.01	10	0.01	2.5	148	0.01
KL28-08	980.5	983.5	0.26	2600	0.06	0.8	25	5	1	30	0.01	10	0.01	2.8	129	0.01
KL28-08	983.5	986.5	0.3	3000	0.05	0.9	33	5	0.01	49	0.01	13	0.01	3.1	104	0.01
KL28-08	986.5	988.7	0.28	2800	0.04	0.8	24	6	1	31	0.01	13	0.01	3.0	141	0.01
KL28-08	988.7	991.7	0.27	2700	0.05	0.6	22	6	1	38	0.01	11	0.01	2.9	106	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL28-08	991.7	994.8	0.354	3540	0.08	0.7	21	5	1	22	0.01	7	0.01	2.0	95	0.01
KL28-08	994.8	997.9	0.5	5000	0.16	0.9	29	10	0.01	46	0.01	8	0.01	3.3	78	0.01
KL28-08	997.9	1001	0.23	2300	0.08	0.5	22	11	3	39	1	15	0.01	4.1	112	0.01
KL28-08	1001	1004.1	0.292	2920	0.07	0.8	26	10	0.01	64	0.01	11	0.01	2.8	95	0.01
KL28-08	1004.1	1007.2	0.355	3550	0.06	0.9	26	6	0.01	40	0.01	9	0.01	2.7	79	0.01
KL28-08	1007.2	1010.3	0.3	3000	0.07	0.9	23	5	0.01	49	0.01	9	0.01	2.6	82	0.01
KL28-08	1010.3	1013.5	0.367	3670	0.08	0.9	26	6	0.01	52	0.01	11	0.01	2.5	87	0.01
KL28-08	1013.5	1015.3	0.517	5170	0.09	1.2	25	7	1	82	2	10	0.01	3.0	83	0.01
KL28-08	1015.3	1018.4	0.29	2900	0.08	1.2	30	8	3	40	0.01	10	0.01	2.5	73	0.01
KL28-08	1018.4	1021.5	0.3	3000	0.07	0.1	37	7	2	58	0.01	7	0.01	2.3	78	0.01
KL28-08	1021.5	1024	0.29	2900	0.09	0.1	35	8	3	52	0.01	9	0.01	2.5	80	0.01
KL28-09	0	3.2	0.0012	12	0.01	3.6	1050	3400	10	3	0.01	1	6.1	4.8	14	0.01
KL28-09	3.2	6.2	0.0013	13	0.03	2.5	470	1920	30	2	0.01	1	3.5	3.5	13	0.01
KL28-09	6.2	9.2	0.0037	37	0.02	6.3	1140	4000	32	3	0.01	1	9	6.5	14	0.01
KL28-09	9.2	12.2	0.0014	14	0.01	2.4	690	1220	17	2	2	1	2.4	5.3	14	0.01
KL28-09	12.2	15.2	0.0009	9	0.01	1	500	540	7	3	0.01	1	1.4	1.8	17	0.01
KL28-09	15.2	18.2	0.0014	14	0.01	1.8	660	650	8	3	0.01	1	2.4	4.0	17	0.01
KL28-09	18.2	21.2	0.0011	11	0.01	1.7	700	840	7	2	0.01	1	2.7	3.0	15	0.01
KL28-09	21.2	24.2	0.0015	15	0.01	2.2	1220	1710	11	2	1	1	3.4	5.3	17	0.01
KL28-09	24.2	26.7	0.003	30	0.01	3.5	1660	2040	14	1	4	1	3.5	4.5	19	0.01
KL28-09	26.7	29.7	0.0015	15	0.01	2.5	1150	1160	13	1	3	3	2.2	5.8	19	0.01
KL28-09	29.7	32.7	0.0029	29	0.08	5.9	2690	6100	33	3	0.01	1	7.1	10.2	13	0.01
KL28-09	32.7	35.7	0.0014	14	0.01	1.5	770	780	16	2	0.01	2	2.3	3.1	15	0.01
KL28-09	35.7	38.7	0.0011	11	0.01	1.6	710	1210	14	4	0.01	1	2	2.5	14	0.01
KL28-09	38.7	40.7	0.0025	25	0.01	2.7	1580	1910	19	3	0.01	1	3.8	8.8	13	0.01
KL28-09	40.7	42.7	0.0123	123	0.01	18	7300	9800	44	4	0.01	1	67	12.5	15	0.01
KL28-09	42.7	45.2	0.0072	72	0.01	8.8	9000	9200	34	4	1	1	13.5	14.0	16	0.01
KL28-09	45.2	48.2	0.0036	36	0.01	5.2	2580	4480	21	4	2	1	7	9.8	20	0.01
KL28-09	48.2	51.2	0.0042	42	0.09	3.9	1610	1660	90	3	1	1	6.3	9.0	16	0.01
KL28-09	51.2	54.2	0.0036	36	0.03	3.4	3320	2360	41	3	1	1	4.4	12.0	15	0.01
KL28-09	54.2	57.2	0.0026	26	0.01	0.6	340	367	6	1	0.01	1	1.1	3.5	17	0.01
KL28-09	57.2	60.2	0.0015	15	0.01	1.6	890	1160	6	2	0.01	1	2.3	6.1	16	0.01
KL28-09	60.2	63.2	0.0058	58	0.01	2	1820	1690	11	3	1	1	2.6	7.8	23	0.01
KL28-09	63.2	66.2	0.0029	29	0.01	1.2	1200	1040	10	3	0.01	1	1.7	4.8	15	0.01
KL28-09	66.2	69.2	0.0036	36	0.01	1	1590	710	10	2	0.01	1	1.8	1.5	12	0.01
KL28-09	69.2	72.2	0.0021	21	0.02	1.1	1320	790	7	3	0.01	1	1.8	3.5	18	0.01
KL28-09	72.2	75.2	0.0074	74	0.02	6.7	5200	6400	29	10	6	1	8.8	10.3	19	0.01
KL28-09	75.2	78.2	0.0068	68	0.01	2.1	1680	1420	10	5	2	1	2.4	4.5	18	0.01
KL28-09	78.2	81.2	0.0034	34	0.01	2.9	3630	1980	15	4	3	1	3	6.5	20	0.01
KL28-09	81.2	84.2	0.0037	37	0.01	4.8	2970	2980	15	6	7	1	3.9	7.4	16	0.01
KL28-09	84.2	87.2	0.0026	26	0.01	3.8	1490	1050	16	12	13	1	1.3	10.8	14	0.01
KL28-09	87.2	90.2	0.0039	39	0.01	6.2	3170	1720	17	11	20	1	2.4	3.8	20	0.01
KL28-09	90.2	93.2	0.005	50	0.01	3.8	2060	1170	22	8	16	1	2	8.8	27	0.01
KL28-09	93.2	96.2	0.0045	45	0.01	3.6	2550	1270	13	6	8	1	1	7.3	18	0.01
KL28-09	96.2	99.2	0.0074	74	0.01	3.8	7100	1950	35	7	10	1	3.2	10.3	16	0.01
KL28-09	99.2	102.2	0.0111	111	0.01	3.7	2850	1380	39	8	12	1	5.2	4.3	18	0.01
KL28-09	102.2	105.2	0.0062	62	0.01	2.4	1740	1020	26	8	6	1	4.5	4.8	23	0.01
KL28-09	105.2	108.2	0.0038	38	0.01	2.2	2100	830	26	7	5	1	2.8	2.8	21	0.01
KL28-09	108.2	111.2	0.0104	104	0.01	4	4480	1630	32	16	13	1	3.3	5.3	23	0.01
KL28-09	111.2	114.2	0.0281	281	0.04	3.5	4800	2120	52	12	10	2	3.4	8.3	19	0.01
KL28-09	114.2	117.2	0.054	540	0.11	5.7	7700	2400	120	11	23	10	2.4	19.0	36	0.01
KL28-09	117.2	120.2	0.185	1850	0.15	4.8	3170	2500	120	10	12	28	3.9	27.7	49	0.01
KL28-09	120.2	123.2	0.047	470	0.13	1.1	1020	347	120	3	17	25	2.2	14.5	37	0.01
KL28-09	123.2	126.2	0.066	660	0.14	2.2	740	142	110	1	7	12	2.1	13.8	36	0.01
KL28-09	126.2	129.2	0.052	520	0.05	1.3	262	271	81	64	7	12	3.1	15.3	37	0.01
KL28-09	129.2	132.2	0.195	1950	0.13	1	258	260	74	7	2	12	2.5	10.6	48	0.01
KL28-09	132.2	135.2	0.072	720	0.17	1.2	295	294	37	6	31	7	2.1	15.0	46	0.01
KL28-09	135.2	138.2	0.0154	154	0.08	0.8	120	103	91	245	7	12	1.2	40.5	29	0.01
KL28-09	138.2	141.2	0.055	550	0.12	0.9	4280	78	45	60	7	23	2.5	18.5	47	0.01
KL28-09	141.2	144.2	0.056	560	0.11	1.7	1600	342	65	33	16	10	2.1	10.0	35	0.01
KL28-09	144.2	147.2	0.102	1020	0.47	9.6	1130	1550	47	3	43	7	2.2	15.3	40	0.01
KL28-09	147.2	150.2	0.037	370	0.14	2.3	1430	510	41	9	30	4	1.8	12.3	35	0.01
KL28-09	150.2	153.2	0.015	150	0.04	1	520	304	30	6	9	2	1.2	11.0	21	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL28-09	153.2	155.2	0.0116	116	0.04	1.4	550	352	28	8	12	1	1.9	5.5	25	0.01
KL28-09	155.2	156.2	0.54	5400	0.43	27	9000	3300	53	14	72	3	6.6	55.0	54	0.01
KL28-09	156.2	159.2	0.82	8200	1.67	33.5	9300	2900	65	21	108	6	2.4	84.0	73	0.01
KL28-09	159.2	162.2	0.043	430	0.04	2.9	1580	1330	34	35	35	3	5.5	8.3	34	0.01
KL28-09	162.2	165.2	0.0319	319	0.12	4.5	7200	5000	50	15	22	1	3.6	15.7	34	0.01
KL28-09	165.2	168.2	0.23	2300	0.36	3.1	331	420	41	82	30	9	5.1	44.0	187	0.01
KL28-09	168.2	171.2	0.177	1770	0.17	2.2	620	420	40	71	8	12	5	12.8	126	0.01
KL28-09	171.2	172.8	0.44	4400	0.16	2.5	148	73	32	189	7	27	3.4	13.3	137	0.01
KL28-09	172.8	174.8	0.208	2080	0.15	1.4	206	316	8	161	7	15	1.5	16.8	169	0.01
KL28-09	174.8	176.7	0.98	9800	0.28	4.7	126	235	38	970	7	18	4	73.0	74	0.01
KL28-09	176.7	179.7	0.8	8000	0.52	6.7	500	343	43	376	8	33	3.4	48.0	200	0.01
KL28-09	179.7	182.7	0.4	4000	0.11	4	198	332	11	29	4	13	1.8	19.8	165	0.01
KL28-09	182.7	185.7	0.26	2600	0.65	1	1230	27	10	60	5	13	0.5	14.0	64	0.01
KL28-09	185.7	188.7	0.059	590	0.02	1.9	242	97	19	156	4	5	1.4	12.3	38	0.01
KL28-09	188.7	190.7	0.149	1490	0.02	2.2	241	137	15	124	5	6	1.4	11.3	44	0.01
KL28-09	190.7	192.8	0.15	1500	0.06	2	242	100	31	13	10	3	0.3	12.3	48	0.01
KL28-09	192.8	195.2	0.099	990	0.21	4.1	295	250	33	1970	30	7	1.1	17.4	51	0.01
KL28-09	195.2	198.2	0.73	7300	0.27	11.2	126	145	41	580	8	38	0.2	34.5	34	0.01
KL28-09	198.2	201.2	1.77	17700	0.9	21.1	234	244	35	520	10	93	0.8	59.0	64	0.01
KL28-09	201.2	204.2	0.89	8900	1.03	13.5	2100	273	36	66	160	40	1.6	36.5	51	0.01
KL28-09	204.2	206.6	1.49	14900	1.72	42.8	11500	1210	48	350	102	88	26.2	39.0	130	0.01
KL28-09	206.6	208	0.5	5000	2.52	38.3	21300	5100	22	85	142	30	25.2	42.0	123	0.01
KL28-09	208	210.2	0.05	500	0.11	1.9	1850	730	9	45	5	5	1	5.5	31	0.01
KL28-09	210.2	213.2	0.0258	258	0.04	3.8	5200	2560	15	66	19	3	1.2	16.0	39	0.01
KL28-09	213.2	216.2	0.025	250	0.04	3.1	9700	1420	16	19	30	2	1.4	12.0	33	0.01
KL28-09	216.2	219.2	0.234	2340	0.08	9.7	4200	2540	13	49	15	3	3.4	13.5	30	0.01
KL28-09	219.2	222.2	0.0095	95	0.03	1.6	1560	450	3	19	5	1	0.2	5.3	32	0.01
KL28-09	222.2	225.2	0.0047	47	0.01	1.4	520	500	4	20	3	2	0.9	1.6	25	0.01
KL28-09	225.2	226.7	0.0032	32	0.01	1.6	338	520	2	10	4	1	0.01	1.3	26	0.01
KL28-09	226.7	229.7	0.026	260	0.05	4.5	8000	1040	18	290	19	3	2.1	9.5	41	0.01
KL28-09	229.7	232.7	0.0071	71	0.01	2.8	960	1050	5	9	6	1	0.2	5.5	31	0.01
KL28-09	232.7	235.7	0.0083	83	0.01	2.1	580	1390	5	45	5	1	0.4	10.5	28	0.01
KL28-09	235.7	237.7	0.018	180	0.3	9.3	4800	9100	11	22	6	1	1.8	58.0	22	0.01
KL28-09	237.7	239.8	0.0085	85	0.01	1.1	1010	490	4	15	2	1	0.01	3.3	16	0.01
KL28-09	239.8	242.2	0.0371	371	0.04	1.2	1580	640	14	18	5	1	1	9.8	19	0.01
KL28-09	242.2	245.2	0.107	1070	0.04	5.1	2080	3220	7	19	23	1	2.5	28.5	18	0.01
KL28-09	245.2	248.2	0.0074	74	0.03	1.9	600	830	4	12	4	1	0.2	6.0	18	0.01
KL28-09	248.2	251.2	0.0168	168	0.03	1.4	1140	620	5	15	3	1	0.5	4.3	19	0.01
KL28-09	251.2	254.2	0.0129	129	0.03	1	329	300	7	17	3	1	0.3	3.8	14	0.01
KL28-09	254.2	256.5	1.33	13300	3.89	1.9	338	53	2	2	3	21	0.2	21.5	35	0.01
KL28-09	256.5	258.2	0.0214	214	0.06	10.1	3900	3290	10	36	26	1	0.8	21.4	24	0.01
KL28-09	258.2	261.2	0.0065	65	0.01	0.8	372	407	4	21	2	1	0.01	4.3	27	0.01
KL28-09	261.2	263.7	0.0091	91	0.05	3.7	740	1050	6	27	20	1	0.4	12.5	24	0.01
KL28-09	263.7	266.7	0.0086	86	0.28	1.9	1060	327	3	18	18	1	0.01	5.3	21	0.01
KL28-09	266.7	269.7	0.0294	294	0.04	0.1	1480	44	6	6	1	1	0.01	2.5	21	0.01
KL28-09	269.7	272.7	0.0217	217	0.03	0.6	3060	101	7	5	3	1	0.4	4.5	18	0.01
KL28-09	272.7	275.7	0.26	2600	0.2	1.9	21200	220	10	5	4	6	10.1	36.0	23	0.01
KL28-09	275.7	278.7	0.0371	371	0.08	1.7	5800	560	9	4	12	1	3.1	10.8	15	0.01
KL28-09	278.7	280.2	0.0113	113	0.03	1.4	2460	460	17	5	3	1	0.8	6.5	19	0.01
KL28-09	280.2	282.2	0.0302	302	0.06	1	2360	610	13	21	5	1	0.5	5.3	20	0.01
KL28-09	282.2	285.2	0.24	2400	0.31	2.9	2190	318	11	4	8	4	0.7	11.3	22	0.01
KL28-09	285.2	288.2	0.495	4950	0.71	22.5	71000	6560	27	190	20	15	1.4	88.0	24	0.39
KL28-09	288.2	291.2	0.126	1260	0.2	2.5	6800	740	59	9	11	7	1.2	8.5	24	0.01
KL28-09	291.2	294.2	0.476	4760	0.5	3.7	1630	267	16	6	22	3	1.1	10.8	19	0.01
KL28-09	294.2	297.2	0.0156	156	0.06	0.6	1880	710	13	6	8	1	0.5	8.8	20	0.01
KL28-09	297.2	300.2	0.0257	257	0.04	1.1	590	382	8	6	8	1	0.01	7.3	19	0.01
KL28-09	300.2	302.6	0.0153	153	0.03	0.1	421	57	12	2	1	1	0.01	2.0	23	0.01
KL28-09	302.6	304.3	2.19	21900	3.11	4	24600	14	2	6	16	40	2.9	30.0	33	0.01
KL28-09	304.3	306.2	0.0097	97	0.05	5	770	840	5	6	22	1	0.01	10.3	15	0.01
KL28-09	306.2	309.2	0.468	4680	1.36	1.3	376	24	3	7	12	16	0.01	10.8	34	0.01
KL28-09	309.2	312.2	0.57	5700	0.13	5.7	113	76	31	46	3	31	0.6	34.8	234	0.01
KL28-09	312.2	315.2	0.077	770	0.38	0.1	87	21	13	186	4	3	0.01	4.8	73	0.01
KL28-09	315.2	318.2	0.125	1250	0.42	0.7	48	25	37	318	6	2	0.01	4.8	75	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL28-09	318.2	321.2	0.22	2200	0.55	0.6	50	19	15	750	5	4	0.01	8.0	80	0.01
KL28-09	321.2	324.2	0.479	4790	0.79	1	365	27	24	68	13	6	0.01	10.5	86	0.01
KL28-09	324.2	327.2	1.19	11900	1.25	1.6	840	18	8	29	3	21	0.01	26.5	24	0.01
KL28-09	327.2	330.2	0.402	4020	0.56	0.6	97	16	4	20	4	12	0.01	12.5	45	0.01
KL28-09	330.2	333.2	0.275	2750	0.35	0.1	54	13	5	560	2	3	0.01	9.3	19	0.01
KL28-09	333.2	336.2	0.61	6100	0.61	0.8	210	11	7	590	2	24	0.01	31.2	19	0.01
KL28-09	336.2	339.2	0.368	3680	0.49	0.6	86	13	14	500	8	6	0.01	11.0	33	0.01
KL28-09	339.2	342.2	0.24	2400	0.42	0.1	82	10	11	129	2	2	0.01	8.6	30	0.01
KL28-09	342.2	345.2	1.3	13000	0.98	1.9	123	16	4	16	5	4	0.01	28.0	21	0.01
KL28-09	345.2	348.2	0.194	1940	0.31	0.9	57	10	7	38	2	4	0.01	10.0	18	0.01
KL28-09	348.2	351.2	0.156	1560	0.19	0.7	37	9	16	97	1	4	0.01	7.0	25	0.01
KL28-09	351.2	354.2	0.51	5100	0.73	0.1	138	11	12	12	3	9	0.01	11.5	35	0.01
KL28-09	354.2	357.2	0.72	7200	0.89	0.8	95	15	8	17	6	14	0.01	21.5	30	0.01
KL28-09	357.2	360.2	0.391	3910	0.97	0.1	54	8	15	18	2	4	0.01	7.6	29	0.01
KL28-09	360.2	363.2	0.23	2300	0.48	1	216	17	16	29	4	9	0.01	16.5	27	0.01
KL28-09	363.2	366.2	0.356	3560	0.83	0.6	226	11	2	43	5	25	0.01	11.3	20	0.01
KL28-09	366.2	369.2	0.415	4150	0.67	1.3	71	17	33	40	6	4	0.01	6.5	52	0.01
KL28-09	369.2	372.2	0.299	2990	0.54	0.8	42	11	37	21	4	4	0.01	6.8	33	0.01
KL28-09	372.2	375.2	0.22	2200	0.46	0.8	101	13	19	500	4	6	0.01	7.0	74	0.01
KL28-09	375.2	378.2	0.33	3300	2.64	1.2	13600	17	21	430	74	17	0.01	23.0	63	0.01
KL28-09	378.2	381.2	3.35	33500	3	4.3	930	16	4	7	6	14	0.01	21.0	80	0.12
KL28-09	381.2	384.2	2.04	20400	2.62	2.6	1220	10	4	17	4	17	0.01	27.0	40	0.01
KL28-09	384.2	387.2	0.45	4500	1	0.6	162	8	1	3	2	17	0.01	7.5	20	0.01
KL28-09	387.2	390.2	0.93	9300	2.33	1.4	163	7	1	2	2	22	0.01	8.0	20	0.01
KL28-09	390.2	393.2	3.38	33800	4.06	3.2	271	9	0.01	4	1	21	0.01	34.0	26	0.01
KL28-09	393.2	396.2	2.81	28100	4.55	5.4	2700	17	1	3	7	20	0.01	32.0	22	0.01
KL28-09	396.2	399.2	0.74	7400	1.05	1.3	14000	24	1	6	4	16	0.01	18.0	17	0.01
KL28-09	399.2	402.2	0.451	4510	0.42	0.8	740	22	2	3	5	21	0.01	9.0	26	0.01
KL28-09	402.2	405.2	2.13	21300	1.95	3.9	520	21	1	7	4	25	0.01	20.0	28	0.01
KL28-09	405.2	408.2	1.52	15200	1.32	6.2	15200	19	3	45	5	21	0.01	20.0	56	0.01
KL28-09	408.2	411.2	0.83	8300	1.8	26.9	25300	800	16	14	51	13	0.01	35.5	38	0.01
KL28-09	411.2	414.2	0.386	3860	1.87	5.3	3510	47	28	5	46	5	0.3	28.0	40	0.01
KL28-09	414.2	417.2	0.389	3890	1.23	1.7	3420	18	6	5	22	13	0.01	8.6	46	0.01
KL28-09	417.2	420.2	2.94	29400	2.03	3.6	394	11	6	45	1	20	0.01	9.0	62	0.01
KL28-09	420.2	423.2	2.09	20900	1.32	4	287	7	4	7	1	18	0.01	6.0	51	0.01
KL28-09	423.2	426.2	0.72	7200	0.69	1.8	126	9	2	47	1	23	0.01	10.5	47	0.01
KL28-09	426.2	429.2	1.7	17000	1.92	2.9	92	24	7	68	3	13	0.01	19.0	126	0.01
KL28-09	429.2	430.9	0.91	9100	1.41	1.7	30	10	3	74	1	11	0.01	7.3	100	0.01
KL28-09	430.9	432.5	0.69	6900	0.9	1.4	27	7	2	65	2	9	0.01	5.8	87	0.01
KL28-09	432.5	435.2	0.59	5900	0.71	1.5	49	8	1	54	2	6	0.01	5.9	83	0.01
KL28-09	435.2	438.2	0.67	6700	0.44	1.6	30	8	1	114	1	10	0.01	7.0	89	0.01
KL28-09	438.2	441.2	0.73	7300	0.44	1.4	37	6	1	77	0.01	15	0.01	6.5	107	0.01
KL28-09	441.2	444.2	0.465	4650	0.29	1.1	32	6	1	84	0.01	13	0.01	6.3	121	0.01
KL28-09	444.2	447.2	0.86	8600	0.63	1.8	36	7	1	236	1	12	0.01	7.9	122	0.01
KL28-09	447.2	450.2	0.91	9100	0.57	1.8	43	6	1	267	0.01	21	0.01	7.7	79	0.01
KL28-09	450.2	453.2	0.91	9100	0.61	1.9	44	6	1	398	0.01	22	0.01	9.0	78	0.01
KL28-09	453.2	456.2	0.95	9500	0.58	1.8	48	7	1	224	0.01	23	0.01	7.8	119	0.01
KL28-09	456.2	459.2	0.78	7800	0.52	1.3	35	7	2	142	0.01	16	0.01	9.8	146	0.01
KL28-09	459.2	462.2	0.56	5600	0.37	1.1	34	6	0.01	296	0.01	10	0.01	7.8	137	0.01
KL28-09	462.2	465.2	0.74	7400	0.48	1.5	43	6	1	287	0.01	15	0.01	8.0	138	0.01
KL28-09	465.2	468.2	0.473	4730	0.35	1	40	7	1	112	0.01	12	3.6	7.3	108	0.01
KL28-09	468.2	471.2	0.6	6000	0.49	1.5	36	6	1	115	0.01	13	0.01	7.3	119	0.01
KL28-09	471.2	474.2	0.64	6400	0.71	1.2	28	8	1	116	0.01	9	0.01	6.8	107	0.01
KL28-09	474.2	477.2	1.12	11200	1.65	2.1	30	9	1	63	2	10	0.01	10.3	100	0.01
KL28-09	477.2	480.2	0.58	5800	0.35	1.3	41	8	0.01	92	0.01	14	0.01	6.4	80	0.01
KL28-09	480.2	483.2	0.476	4760	0.34	1.3	51	9	1	54	1	12	0.01	6.0	93	0.01
KL28-09	483.2	486.2	0.46	4600	0.29	1.2	56	9	0.01	167	0.01	11	0.01	8.0	114	0.01
KL28-09	486.2	489.2	0.55	5500	0.34	1.3	77	11	1	110	0.01	14	0.01	7.5	93	0.01
KL28-09	489.2	492.2	0.6	6000	0.43	1.5	63	8	0.01	148	0.01	14	0.01	6.3	113	0.01
KL28-09	492.2	495.2	0.365	3650	0.25	0.7	57	11	0.01	40	0.01	9	0.01	5.0	77	0.01
KL28-09	495.2	498.2	0.238	2380	0.15	0.8	45	7	0.01	25	0.01	7	0.01	5.5	78	0.01
KL28-09	498.2	501.2	0.421	4210	0.3	1	44	9	0.01	51	0.01	8	0.01	5.8	110	0.01
KL30-01	0	3	0.0048	48	0.01	0.1	26	19	7	2	0.01	2	0.4	1.3	8	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL30-01	3	6	0.0041		41	0.01	0.1	42	20	10	2	0.01	1	0.6	1.5	13	0.01
KL30-01	6	9	0.0034		34	0.01	0.1	121	52	9	2	0.01	1	1.1	1.3	16	0.01
KL30-01	9	12	0.0032		32	0.01	0.8	382	272	11	3	0.01	1	1.7	2.0	16	0.01
KL30-01	12	15	0.0023		23	0.01	0.6	91	55	10	3	0.01	3	1	1.5	19	0.01
KL30-01	15	18	0.0026		26	0.01	1.2	62	260	12	1	0.01	2	1.3	2.5	15	0.01
KL30-01	18	21	0.0034		34	0.01	1.7	101	200	14	3	0.01	1	3.5	2.8	22	0.01
KL30-01	21	24	0.0041		41	0.04	1	101	110	18	6	0.01	1	1.9	2.8	25	0.01
KL30-01	24	27	0.0057		57	0.03	18.6	130	9000	21	39	5	1	17	20.6	25	0.01
KL30-01	27	30	0.0018		18	0.07	3.5	113	1270	12	3	0.01	2	4.2	3.5	17	0.01
KL30-01	30	33	0.0017		17	0.13	2.1	165	480	14	4	0.01	1	6.3	3.0	26	0.01
KL30-01	33	36	0.0016		16	0.14	6.4	182	2230	18	2	0.01	2	7	9.8	33	0.01
KL30-01	36	39	0.0037		37	0.02	1.4	283	530	8	3	0.01	2	1.6	2.0	19	0.01
KL30-01	39	42	0.004		40	0.03	2.3	540	3760	4	3	0.01	2	3.4	5.5	7	0.01
KL30-01	42	45	0.0035		35	0.01	1.2	145	307	13	3	0.01	1	1.7	1.3	34	0.01
KL30-01	45	48	0.004		40	0.01	1.4	200	460	28	4	0.01	1	3.4	1.8	25	0.01
KL30-01	48	51	0.0188		188	0.06	4.7	580	4100	33	11	2	3	10.3	6.5	72	0.01
KL30-01	51	54	0.1		1000	0.1	5.6	480	4300	47	32	1	5	10.1	3.8	133	0.01
KL30-01	54	56.5	0.078		780	0.16	4.1	206	770	240	46	4	6	5.9	5.0	79	0.01
KL30-01	56.5	58.5	0.135		1350	0.19	7.3	260	218	360	26	6	8	8.6	8.0	54	0.01
KL30-01	58.5	61.5	0.031		310	0.1	7.6	2000	570	62	17	32	2	3.1	17.0	33	0.01
KL30-01	61.5	64.5	0.21		2100	0.42	238	1200	8200	680	27	575	7	17.9	331.0	72	0.01
KL30-01	64.5	67.5	0.048		480	0.09	4.4	163	145	110	16	5	1	4.5	1.5	48	0.01
KL30-01	67.5	70.5	0.0338		338	0.09	3.6	347	328	39	21	6	1	5.6	6.0	80	0.01
KL30-01	70.5	73.5	0.016		160	0.08	2	268	240	22	14	2	1	2.3	4.3	47	0.01
KL30-01	73.5	76.5	0.016		160	0.09	1.9	490	670	15	11	1	1	3	2.5	34	0.01
KL30-01	76.5	79.5	0.0163		163	0.06	1.7	700	410	17	11	0.01	1	2.8	2.8	32	0.01
KL30-01	79.5	82.5	0.0122		122	0.02	1.4	173	129	7	13	0.01	1	0.9	1.5	27	0.01
KL30-01	82.5	85.5	0.0146		146	0.04	1.1	130	138	14	7	1	1	3.1	0.9	28	0.01
KL30-01	85.5	88.5	0.0106		106	0.1	0.8	63	326	11	7	0.01	1	3.3	0.0	17	0.01
KL30-01	88.5	91.5	0.0132		132	0.03	1.3	79	190	12	6	2	1	2.6	1.3	9	0.01
KL30-01	91.5	94.5	0.0068		68	0.06	1.1	95	376	14	7	0.01	1	3	0.6	13	0.01
KL30-01	94.5	97.5	0.009		90	0.2	4.1	145	1600	21	13	0.01	1	5.4	3.0	18	0.01
KL30-01	97.5	99	0.0152		152	3.22	29.9	450	9600	260	33	18	25	30	72.5	61	0.01
KL30-01	99	101.6	0.0283		283	0.57	37.4	3600	23000	62	21	16	3	42	10.2	57	0.01
KL30-01	101.6	104.5	0.0026		26	0.22	4	122	540	14	7	3	1	2.3	2.8	37	0.01
KL30-01	104.5	109.5	0.003		30	0.08	1.3	450	165	8	7	0.01	1	0.9	1.5	13	0.01
KL30-01	109.5	113	0.0049		49	0.06	2.3	279	770	6	4	0.01	1	2.2	2.0	11	0.01
KL30-01	113	115.7	0.002		20	0.03	0.6	115	200	3	2	0.01	1	0.5	1.0	14	0.01
KL30-01	115.7	118.5	0.005		50	0.04	3.1	2050	1900	8	4	0.01	1	3.7	4.7	19	0.01
KL30-01	118.5	123	0.0021		21	0.07	0.9	112	187	5	3	0.01	1	0.9	1.3	14	0.01
KL30-01	123	126	0.0016		16	0.04	0.1	76	82	2	4	0.01	1	0.5	0.7	14	0.01
KL30-01	126	130.5	0.0013		13	0.02	0.6	65	70	2	1	0.01	1	0.01	1.5	22	0.01
KL30-01	130.5	133.5	0.06		600	0.05	0.8	189	318	4	1	0.01	3	1.2	1.3	27	0.01
KL30-01	133.5	136.5	0.0017		17	0.06	0.7	460	280	6	1	0.01	1	0.3	1.0	25	0.01
KL30-01	136.5	139.5	0.0248		248	0.1	18.9	10100	13200	36	2	3	1	17.7	8.0	26	0.46
KL30-01	139.5	142.5	0.0175		175	0.06	8.4	5550	6500	18	5	1	1	9.3	6.3	29	0.01
KL30-01	142.5	146.3	0.0134		134	0.06	5.1	8450	3600	16	6	0.01	1	5.6	5.5	24	0.01
KL30-01	146.3	149.2	0.0009		9	0.12	2	610	880	14	9	0.01	1	5.3	1.8	13	0.01
KL30-01	149.2	152.9	0.0049		49	0.05	7.5	1370	4030	16	71	11	1	3.8	6.4	11	0.01
KL30-01	152.9	156	0.006		60	0.03	2.1	1230	1670	11	4	0.01	1	2.9	1.0	15	0.01
KL30-01	156	163.5	0.0159		159	0.05	4.6	750	2160	16	11	0.01	2	5.1	2.0	18	0.01
KL30-01	163.5	169.5	0.0151		151	0.06	8.7	2470	2850	17	7	1	2	9.6	4.8	16	0.01
KL30-01	169.5	175.5	0.0151		151	0.11	60.2	8500	10500	38	62	100	2	11.7	37.8	19	0.22
KL30-01	175.5	181.5	0.0215		215	0.09	30.6	9400	24100	27	22	14	2	27	15.4	18	0.01
KL30-01	181.5	186	0.0122		122	0.07	4.9	3540	2100	20	6	6	1	2.7	5.0	14	0.01
KL30-01	186	190.5	0.0208		208	0.09	5.6	4070	1690	38	11	4	1	9.1	2.5	20	0.01
KL30-01	190.5	193.5	0.0183		183	0.18	4.4	1630	1620	26	11	6	1	3.2	3.0	22	0.27
KL30-01	193.5	196.5	0.062		620	0.77	6.2	3120	1880	140	85	63	4	7.1	9.3	41	0.21
KL30-01	196.5	199.5	0.065		650	0.27	8.6	5400	3890	49	21	14	3	6.2	6.5	28	0.13
KL30-01	199.5	202.5	0.12		1200	0.8	10.6	9000	5400	110	31	36	3	2.6	10.0	25	0.15
KL30-01	202.5	205.3	0.225		2250	0.52	4.3	620	570	220	23	13	3	2.6	13.8	32	0.01
KL30-01	205.3	208.5	0.27		2700	0.76	4.3	450	262	130	11	10	3	1.2	9.7	32	0.01
KL30-01	208.5	211.5	0.77		7700	2.08	8.6	890	400	60	24	10	8	2.5	29.5	56	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL30-01	211.5	214.5	0.83	8300	1.14	10.7	2100	460	52	18	15	9	0.9	35.8	48	0.01
KL30-01	214.5	217.5	0.84	8400	1.18	12.1	1650	252	120	150	96	18	3.4	63.0	72	0.01
KL30-01	217.5	220.2	0.82	8200	0.79	3.1	184	134	110	4950	14	20	1.6	25.5	249	0.01
KL30-01	220.2	221.8	0.36	3600	0.61	2.7	288	115	55	1420	36	22	1.2	24.0	216	0.28
KL30-01	221.8	224	0.344	3440	0.48	3	121	67	29	1830	48	12	1.1	14.0	159	0.1
KL30-01	224	226.5	0.72	7200	0.66	8.3	247	73	37	352	90	26	2.2	18.0	58	0.01
KL30-01	226.5	228.7	0.75	7500	0.61	9.5	2290	440	30	281	33	25	1.5	14.0	32	0.01
KL30-01	228.7	230.4	1.04	10400	0.88	5.1	740	275	37	680	7	25	2	14.3	113	0.01
KL30-01	230.4	232.5	0.61	6100	0.86	7	680	234	73	700	8	34	5	40.8	99	0.01
KL30-01	232.5	235.5	2.94	29400	1.39	18.7	3000	193	41	95	6	25	4.4	20.0	34	0.01
KL30-01	235.5	238.5	0.6	6000	1.3	8.6	1900	170	61	99	15	20	4.1	10.7	88	0.01
KL30-01	238.5	241.5	1.18	11800	1.77	14.1	4500	207	64	45	25	20	3.9	19.5	111	0.21
KL30-01	241.5	244.5	0.8	8000	1.13	6.6	900	223	47	201	17	11	6.3	16.5	121	0.01
KL30-01	244.5	247.5	1.55	15500	1.33	9.6	1840	1300	43	242	38	6	6.3	15.0	209	0.25
KL30-01	247.5	250.5	0.78	7800	1.26	8.4	2130	810	57	250	10	36	3.2	42.0	93	0.2
KL30-01	250.5	253.5	1.45	14500	1.76	8.9	1450	382	420	5	6	40	4.4	24.5	75	0.17
KL30-01	253.5	255	0.81	8100	1.3	5.2	1160	290	65	12	8	45	2.5	24.0	70	0.01
KL30-01	255	258	1.76	17600	1.84	6.5	1000	268	53	37	4	49	2.1	29.0	67	0.01
KL30-01	258	261	1.67	16700	1.46	6.7	600	247	16	45	2	32	1.8	15.0	31	0.01
KL30-01	261	264	2.06	20600	1.76	8.6	520	127	14	93	4	36	1.3	28.0	59	0.01
KL30-01	264	267	1.89	18900	2.18	6.8	1710	310	360	23	4	46	6.2	13.0	58	0.01
KL30-01	267	270	1.51	15100	1.33	4.3	820	133	9	13	7	54	1.4	22.0	61	0.01
KL30-01	270	273	3	30000	3.14	7.1	800	73	9	73	2	45	1.7	20.0	52	0.01
KL30-01	273	276	3.16	31600	3.96	6.2	1580	97	16	28	2	61	1.7	23.0	64	0.01
KL30-01	276	279	2.71	27100	2.78	7	2600	54	4	6	5	45	1.4	15.3	28	0.01
KL30-01	279	282	2.27	22700	2.22	8.2	970	40	10	26	7	56	1.1	11.0	61	0.01
KL30-01	282	285	1.88	18800	1.66	7.1	173	26	240	11	7	61	0.9	16.0	133	0.01
KL30-01	285	288	2.34	23400	2.95	7.8	600	43	15	17	5	62	1.3	13.5	93	0.01
KL30-01	288	290.4	2.61	26100	3.68	8.7	1100	45	22	11	5	45	1.9	17.0	83	0.01
KL30-01	290.4	293.4	3.5	35000	3.44	9.8	1570	388	220	30	6	59	1.6	16.5	102	0.01
KL30-01	293.4	296.4	5.01	50100	3.68	15	8300	81	230	195	4	45	1.3	13.0	100	0.01
KL30-01	296.4	298.7	2.26	22600	1.66	4.9	1710	700	860	29	7	46	8.8	36.0	125	0.41
KL30-01	298.7	301.5	2.68	26800	0.58	5.7	720	252	1560	362	1	62	2.2	37.0	201	0.11
KL30-01	301.5	304.5	1.08	10800	0.2	3.3	800	307	1370	1180	0.01	41	2.3	16.0	174	0.24
KL30-01	304.5	307.5	2.56	25600	0.57	6.5	570	317	630	199	0.01	94	1.4	35.0	192	0.18
KL30-01	307.5	310.5	1.18	11800	0.5	2.6	380	157	170	187	0.01	66	0.5	12.3	137	0.27
KL30-01	310.5	313.5	1.46	14600	0.39	3.6	870	530	700	590	0.01	59	1.3	17.5	261	0.38
KL30-01	313.5	316.5	0.6	6000	0.39	1	159	64	43	134	0.01	50	0.01	10.3	93	0.01
KL30-01	316.5	319.5	0.64	6400	0.38	1.6	520	249	130	175	0.01	45	0.01	11.0	141	0.01
KL30-01	319.5	322.5	0.71	7100	0.33	2.2	292	138	170	213	0.01	50	0.7	10.8	147	0.24
KL30-01	322.5	325.5	0.192	1920	0.15	1.3	356	124	210	189	0.01	15	1.9	9.3	126	0.01
KL30-01	325.5	328.5	0.82	8200	0.54	1.5	470	188	47	192	0.01	20	0.8	9.0	175	0.01
KL30-01	328.5	331.5	1.29	12900	0.84	1.8	83	94	170	261	0.01	36	0.5	10.0	195	0.15
KL30-01	331.5	334.5	0.72	7200	0.59	1.5	305	114	60	253	0.01	33	0.01	8.5	160	0.17
KL30-01	334.5	337.5	1.03	10300	0.96	3.2	193	137	210	4500	12	27	1.6	26.0	225	0.11
KL30-01	337.5	340	2.17	21700	0.84	3.7	580	104	13	2510	0.01	32	0.01	11.0	168	0.3
KL30-01	340	343	2.1	21000	0.76	3.2	540	122	18	390	0.01	40	0.3	11.2	184	0.18
KL30-01	343	346.1	1.24	12400	0.79	2	79	70	22	1000	0.01	32	0.01	9.0	153	0.11
KL30-01	346.1	348.5	1.07	10700	0.81	2.3	165	130	21	930	1	37	0.4	11.3	181	0.01
KL30-01	348.5	351	1.23	12300	0.64	2.8	430	110	40	980	0.01	48	0.3	11.5	155	0.18
KL30-01	351	354	2.41	24100	1.24	6.2	251	140	180	1050	0.01	77	0.4	11.0	125	0.13
KL30-01	354	356.5	1.66	16600	1.22	3.6	98	64	38	810	0.01	55	0.4	12.5	123	0.01
KL30-01	356.5	358	1.58	15800	1.29	2.5	60	26	6	610	1	40	0.01	14.0	105	0.01
KL30-01	358	361	5.29	52900	2.07	8.4	118	25	33	2150	3	102	1.3	18.0	112	0.01
KL30-01	361	364	1.99	19900	1.43	3.8	151	34	18	70	5	66	1	17.0	113	0.01
KL30-01	364	366	0.89	8900	1.2	2.7	335	64	29	9	6	65	1.5	13.0	41	0.01
KL30-01	366	369	1.76	17600	1.64	2.8	1000	530	57	181	6	97	2.4	17.0	110	0.01
KL30-01	369	372	1.45	14500	2.17	12.4	8100	70	1350	192	73	42	54	34.0	111	0.01
KL30-01	372	375	3.14	31400	2.43	10.3	2600	2900	68	500	2	60	5.3	17.0	106	0.37
KL30-01	375	378	1.08	10800	1.71	3.4	304	43	19	18	4	313	0.9	19.8	43	0.01
KL30-01	378	381	1.6	16000	1.21	5.8	470	140	290	16	5	116	2.3	25.4	42	0.01
KL30-01	381	384	1.66	16600	1.82	5.6	550	114	45	4	7	110	2.6	30.0	116	0.1
KL30-01	384	387	1.22	12200	1.56	5.5	1050	440	380	7	12	135	2.2	35.5	125	0.16

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL30-01	387	390	1.44	14400	1.26	3.6	310	48	15	390	3	100	0.5	16.0	61	0.12
KL30-01	390	393	1.12	11200	0.93	4.3	2060	399	73	112	5	53	1.5	13.3	158	0.37
KL30-01	393	396	1.13	11300	0.61	4.6	185	56	73	730	4	51	0.8	12.8	126	0.27
KL30-01	396	399	0.72	7200	0.27	1.4	155	46	42	334	2	32	0.6	10.0	105	0.01
KL30-01	399	402	0.249	2490	1.03	1.7	1060	670	430	165	1	27	3.1	15.0	83	0.7
KL30-01	402	405	0.36	3600	0.32	1.1	500	110	310	202	2	36	3.8	18.3	85	0.19
KL30-01	405	408	0.483	4830	0.18	1	162	44	21	136	2	24	1.1	11.0	64	0.01
KL30-01	408	411	0.49	4900	0.32	0.9	106	48	29	127	2	29	0.7	13.0	50	0.01
KL30-01	411	412.8	0.413	4130	0.34	1	200	58	82	116	2	21	1.1	7.3	68	0.01
KL30-01	412.8	414.9	0.71	7100	0.58	3.2	169	57	33	175	7	23	1.2	7.0	82	0.01
KL30-01	414.9	417	0.86	8600	1.36	9.3	372	85	40	82	26	22	1	6.0	60	0.01
KL30-01	417	420	0.372	3720	0.79	7.1	274	92	64	2220	20	17	0.7	10.5	63	0.01
KL30-01	420	423	0.34	3400	0.44	4	199	37	46	368	19	25	0.2	12.5	48	0.01
KL30-01	423	426	0.78	7800	1.08	10	2650	72	66	28	17	28	0.6	14.8	39	0.01
KL30-01	426	429	1.85	18500	2.04	16.6	1820	200	170	12	12	25	1.6	15.3	56	0.01
KL30-01	429	432	1.41	14100	2.03	7.9	750	103	71	28	10	18	1.2	12.3	57	0.01
KL30-01	432	435	2.86	28600	3.79	19	1510	460	210	7	7	40	2	26.0	47	0.11
KL30-01	435	438	1.76	17600	2.05	16.1	1460	1210	340	16	7	17	2.4	24.0	63	0.33
KL30-01	438	441	2.04	20400	1.71	8.4	421	237	74	110	6	32	1.8	19.5	82	0.12
KL30-01	441	444	2.07	20700	1.99	12.3	1380	2500	340	34	7	49	2.3	24.0	87	0.37
KL30-01	444	447	1.83	18300	1.95	8.6	730	301	38	22	7	42	1.6	29.5	88	0.1
KL30-01	447	450	2.14	21400	1.8	7.8	770	174	36	21	7	51	0.9	22.0	70	0.1
KL30-01	450	453	0.88	8800	0.69	2.8	364	121	60	28	6	49	1.6	16.0	66	0.01
KL30-01	453	456	1.98	19800	0.93	3.2	301	81	34	40	3	36	0.9	19.5	43	0.01
KL30-01	456	459	1.92	19200	0.92	5.3	540	164	31	390	5	42	1.1	19.5	72	0.01
KL30-01	459	462	0.64	6400	0.48	4.1	227	87	38	470	8	24	1.1	16.2	123	0.01
KL30-01	462	465	1.8	18000	0.81	9	670	226	50	29	9	30	1.3	22.0	80	0.01
KL30-01	465	468	0.425	4250	0.33	2.4	660	377	48	35	12	20	2.3	16.8	70	0.01
KL30-01	468	471	0.98	9800	0.91	7.3	630	66	45	42	8	19	1	13.8	63	0.01
KL30-01	471	474	1.31	13100	0.99	7.8	4100	4500	62	20	7	30	2.3	18.3	84	0.01
KL30-01	474	476.7	2.2	22000	1.16	9.4	870	430	79	4	6	36	2.4	25.5	59	0.01
KL30-01	476.7	479.8	1.78	17800	1.39	1.8	2500	420	280	3	5	41	1.2	19.0	48	0.01
KL30-01	479.8	482.9	1.47	14700	1.33	7.8	1000	126	52	3	4	54	2.7	8.3	35	0.01
KL30-01	482.9	486	2.4	24000	1.59	27.1	7100	7500	73	30	36	78	6.4	18.0	47	0.01
KL30-01	486	487.6	4.37	43700	2.68	56	5900	510	200	42	50	113	12	27.0	41	0.01
KL30-01	487.6	489.8	2.67	26700	1.73	38	3700	237	46	20	14	70	10.1	32.0	46	0.01
KL30-01	489.8	491.2	1.21	12100	0.53	5.2	12500	1600	100	207	0.01	30	0.6	16.3	49	0.26
KL30-01	491.2	493.2	0.74	7400	0.8	15.4	2170	105	31	32	18	15	0.5	32.0	50	0.01
KL30-01	493.2	495	1.87	18700	1.23	37.1	1460	110	35	82	42	102	1.3	32.0	49	0.01
KL30-01	495	498	3.23	32300	1.44	61	4100	800	23	11	90	114	4.1	28.5	44	0.01
KL30-01	498	501	2.68	26800	1.37	49	7100	1400	30	6	26	69	2.7	36.0	35	0.01
KL30-01	501	504	2.18	21800	1.73	36	48600	4800	56	4	12	54	1	34.0	43	0.01
KL30-01	504	507	2.48	24800	0.93	33.1	4900	680	310	18	4	65	1.5	25.0	27	0.15
KL30-01	507	510	2.03	20300	1.19	25.5	6500	910	780	62	12	52	4.1	52.5	40	0.36
KL30-01	510	513	3.24	32400	0.84	18.8	5600	550	1170	50	6	46	32	108.0	38	0.51
KL30-01	513	516	2.73	27300	0.87	25.1	2080	910	2100	17	6	38	4.8	33.5	48	0.83
KL30-01	516	519	1.75	17500	0.88	17.9	1100	121	65	13	5	52	0.8	25.8	28	0.01
KL30-01	519	521.6	1.83	18300	0.95	38.8	25700	18000	1510	8	9	18	32	38.0	44	1.09
KL30-01	521.6	523.6	1.88	18800	1.64	23	6100	3200	32	62	6	20	0.9	20.5	25	0.01
KL30-01	523.6	525	2.86	28600	1.15	26.1	570	70	6	30	4	26	0.3	37.0	10	0.01
KL30-01	525	528	3.14	31400	1.28	22.4	1840	342	43	252	2	23	1.5	13.0	17	0.01
KL30-01	528	531	2.93	29300	1.01	9.4	260	75	15	108	1	18	0.4	18.0	15	0.01
KL30-01	531	534	1.94	19400	0.31	3.5	206	43	21	73	0.01	24	0.5	12.5	37	0.01
KL30-01	534	537	1.07	10700	0.28	2.3	560	112	79	178	0.01	28	0.9	9.5	48	0.01
KL30-01	537	540	0.87	8700	0.57	17.1	6000	54	24	66	21	13	1.4	25.5	40	0.01
KL30-01	540	543	1.24	12400	0.48	7.7	3200	770	1370	120	1	17	60	10.3	47	0.7
KL30-01	543	546	1.47	14700	0.38	3	480	82	160	269	0.01	35	2.1	13.0	68	0.01
KL30-01	546	549	0.88	8800	0.59	2.6	205	57	13	51	0.01	19	0.3	10.0	35	0.01
KL30-01	549	552	1.7	17000	0.28	3	600	99	45	89	2	43	0.9	15.5	76	0.13
KL30-01	552	555	0.6	6000	0.3	1.6	161	57	7	28	0.01	42	1	18.1	44	0.01
KL30-01	555	558	0.463	4630	0.14	1.4	47	21	2	54	0.01	20	0.01	11.3	44	0.01
KL30-01	558	561	0.58	5800	0.21	1.6	73	24	7	710	0.01	47	0.3	17.0	34	0.01
KL30-01	561	564	0.44	4400	0.24	1.4	87	13	7	16	0.01	34	0.01	9.3	39	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL30-01	564	567	0.123	1230	0.11	0.1	70	14	3	7	0.01	10	0.3	1.4	47	0.01
KL30-01	567	570	1.15	11500	0.44	2.1	106	26	4	48	0.01	41	1.1	14.0	34	0.01
KL30-01	570	573	0.471	4710	0.19	1.4	61	16	6	65	0.01	16	0.01	7.9	50	0.01
KL30-01	573	576	1.35	13500	0.59	2.1	174	28	9	560	0.01	37	0.2	13.5	63	0.01
KL30-01	576	579	0.97	9700	1.28	3.1	47	13	6	99	0.01	28	0.2	23.5	39	0.01
KL30-01	579	582	0.62	6200	0.37	2.2	181	58	8	102	0.01	17	0.6	8.8	44	0.01
KL30-01	582	583.9	0.77	7700	0.53	2.4	260	40	58	161	0.01	30	0.6	14.5	56	0.01
KL30-01	583.9	586.1	0.95	9500	0.39	2.5	369	84	10	258	1	19	0.4	7.8	78	0.01
KL30-01	586.1	587.9	0.94	9400	0.28	2	154	55	8	399	0.01	25	0.7	9.2	69	0.01
KL30-01	587.9	591	1.21	12100	0.17	2.4	161	51	27	590	2	24	1.2	7.8	118	0.26
KL30-01	591	594	0.491	4910	0.15	1.8	221	50	38	2100	1	18	5	8.0	84	0.19
KL30-01	594	596.5	0.378	3780	0.13	1.2	142	82	20	269	0.01	17	0.8	8.5	84	0.01
KL30-01	596.5	599.5	0.78	7800	0.53	1.8	75	28	16	271	1	60	1.1	28.7	46	0.01
KL30-01	599.5	601.2	1.9	19000	0.63	7.8	270	185	24	35	0.01	16	1.6	16.0	10	0.01
KL30-01	601.2	603	1.3	13000	0.67	3.4	75	24	6	290	0.01	37	0.4	29.0	35	0.01
KL30-01	603	606	1.42	14200	0.45	2	97	36	23	302	1	42	1	14.0	43	0.01
KL30-01	606	609	1.24	12400	0.31	2.1	213	60	130	201	1	24	3.1	7.8	53	0.39
KL30-01	609	612	1.21	12100	0.61	4	1020	128	140	214	0.01	32	0.8	9.3	39	1.62
KL30-01	612	615	1	10000	0.87	2.5	660	105	48	89	1	13	4	7.8	43	0.84
KL30-01	615	618	0.57	5700	1.33	4.5	1890	286	180	104	2	20	0.8	10.0	58	2.12
KL30-01	618	621	1.33	13300	0.6	3.5	780	247	79	620	0.01	44	0.6	9.8	58	1.04
KL30-01	621	624	2.16	21600	0.52	4.6	520	200	450	2000	1	92	1	16.0	85	0.59
KL30-01	624	626.1	0.58	5800	0.56	2.5	870	164	26	283	3	46	0.3	21.8	30	0.15
KL30-01	626.1	628.1	0.481	4810	0.23	3.2	46	16	2	136	0.01	28	0.01	26.5	57	0.01
KL30-01	628.1	630	0.534	5340	0.3	3.3	76	40	9	84	1	20	0.2	15.5	46	0.01
KL30-01	630	633	0.414	4140	0.19	2.1	65	27	20	89	1	9	0.2	12.3	23	0.01
KL30-01	633	636	0.73	7300	0.67	3.3	271	91	18	235	1	17	0.3	17.3	96	0.01
KL30-01	636	639	0.91	9100	0.53	2.6	920	171	12	256	1	46	0.01	27.4	191	0.2
KL30-01	639	642	0.78	7800	0.42	2.7	148	53	50	88	1	29	0.01	47.0	110	0.01
KL30-01	642	645	0.43	4300	0.13	2.5	162	80	14	262	1	13	0.01	18.8	172	0.01
KL30-01	645	647.2	0.63	6300	0.14	3	490	87	49	203	2	12	1.3	14.8	164	0.11
KL30-01	647.2	650.3	0.61	6100	0.12	2.9	213	75	32	56	4	18	0.2	21.8	218	0.01
KL30-01	650.3	652	0.343	3430	0.11	1.5	248	71	21	19	1	8	0.2	9.0	167	0.01
KL30-01	652	654	0.364	3640	0.06	1.4	180	56	8	62	1	16	0.01	15.5	160	0.01
KL30-01	654	657	0.365	3650	0.04	1.5	330	156	15	260	2	24	0.6	24.3	243	0.01
KL30-01	657	660	0.165	1650	0.03	1.3	100	50	4	106	1	26	0.01	31.2	222	0.01
KL30-01	660	663	0.159	1590	0.05	1.1	156	104	0.01	64	0.01	5	0.01	3.2	76	0.01
KL30-01	663	666	0.186	1860	0.06	1.3	55	18	0.01	29	0.01	4	0.01	4.8	29	0.01
KL30-01	666	669	0.484	4840	0.15	2.5	87	26	4	77	0.01	8	0.01	7.0	50	0.01
KL30-01	669	672	0.241	2410	0.06	1.5	86	25	6	179	2	19	0.3	25.9	216	0.01
KL30-01	672	675	0.24	2400	0.05	1.3	135	33	20	211	2	24	0.5	27.7	215	0.01
KL30-01	675	678	1.59	15900	0.55	6.2	146	46	24	185	2	20	0.6	16.8	178	0.01
KL30-01	678	681	1.27	12700	0.39	4.7	920	252	66	98	0.01	42	0.01	10.8	77	0.01
KL30-01	681	684	0.66	6600	0.16	4.1	241	192	81	109	3	16	2.9	15.3	143	0.01
KL30-01	684	687	0.475	4750	0.15	2.6	650	240	12	62	2	16	0.3	17.0	61	0.01
KL30-01	687	690	0.58	5800	0.19	3.4	560	267	34	134	2	19	0.3	15.5	87	0.01
KL30-01	690	693	0.56	5600	0.23	3.5	720	620	28	93	1	17	0.4	13.3	71	0.01
KL30-01	693	696	0.478	4780	0.14	3.2	650	246	43	132	2	10	1.5	10.4	70	0.01
KL30-01	696	699	0.426	4260	0.15	2.4	270	165	7	48	1	14	0.01	21.3	74	0.01
KL30-01	699	702	1.43	14300	1.54	14	4400	2600	330	151	2	62	1.2	51.4	145	0.01
KL30-01	702	704	1.27	12700	0.8	7.1	1890	780	340	343	1	46	0.8	38.1	122	0.01
KL30-01	704	706.1	0.389	3890	0.31	1.8	266	21	47	44	0.01	15	0.01	20.3	28	0.01
KL30-01	706.1	708	0.55	5500	0.47	1.8	55	10	7	6	0.01	9	0.01	8.3	36	0.01
KL30-01	708	711	0.445	4450	0.5	1.2	63	10	6	64	0.01	8	0.01	6.0	21	0.01
KL30-01	711	714	1.21	12100	1.22	3.5	264	20	10	67	0.01	14	0.01	10.0	20	0.01
KL30-01	714	717	0.74	7400	0.58	2.7	112	10	9	39	1	16	0.01	14.0	27	0.01
KL30-01	717	720	0.2	2000	0.08	0.8	57	12	6	40	0.01	9	0.01	9.3	17	0.01
KL30-01	720	723	0.61	6100	0.44	1.8	73	7	6	48	1	13	0.01	15.3	17	0.01
KL30-01	723	726	0.375	3750	0.18	1.5	116	41	7	40	0.01	10	0.01	9.8	12	0.01
KL30-01	726	729	1.15	11500	0.41	4.3	46	8	8	67	1	22	0.01	32.3	24	0.01
KL30-01	729	732	0.197	1970	0.42	1	430	67	6	44	0.01	9	0.01	12.0	102	0.01
KL30-01	732	735	0.156	1560	0.16	1	138	27	5	90	1	5	0.01	5.3	66	0.01
KL30-01	735	738	0.339	3390	0.1	1.3	61	6	9	26	1	9	0.01	6.8	62	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL30-01	738	741	1.87	18700	0.85	4.4	125	7	2	10	1	21	0.01	11.6	34	0.01
KL30-01	741	744	0.149	1490	0.06	0.1	34	6	2	37	1	5	0.01	4.3	16	0.01
KL30-01	744	747	0.128	1280	0.06	0.7	24	6	0.01	34	0.01	5	0.01	6.2	30	0.01
KL30-01	747	750	0.446	4460	0.18	2.4	90	10	3	54	0.01	7	0.01	8.2	25	0.01
KL30-01	750	753	0.263	2630	0.09	1.3	60	6	3	62	0.01	5	0.01	4.6	38	0.01
KL30-01	753	756	0.258	2580	0.13	1.4	32	5	2	10	0.01	6	0.01	2.4	25	0.01
KL30-01	756	759	0.131	1310	0.1	0.9	82	7	3	18	1	7	0.01	2.8	35	0.01
KL30-01	759	762	0.407	4070	0.24	1.7	1430	106	8	17	1	6	0.01	7.6	93	0.01
KL30-01	762	765	0.217	2170	0.09	1.1	42	10	8	43	1	7	0.01	2.8	38	0.01
KL30-01	765	768	0.126	1260	0.14	0.9	34	7	7	108	0.01	5	0.01	3.3	33	0.01
KL30-01	768	771	0.69	6900	0.5	2.6	83	16	10	33	3	7	0.2	7.5	55	0.01
KL30-01	771	774	0.263	2630	0.23	1.4	73	7	8	232	0.01	12	0.01	7.0	66	0.01
KL30-01	774	776.7	0.246	2460	0.33	1.5	470	72	11	20	1	11	0.01	6.5	91	0.01
KL30-01	776.7	779.8	1.15	11500	0.85	5.6	2300	376	22	33	2	14	0.01	13.3	139	0.01
KL30-01	779.8	782.9	0.94	9400	0.46	1.9	950	120	9	208	1	14	0.01	8.3	88	0.01
KL30-01	782.9	785.1	1.34	13400	0.64	2.8	185	13	92	28	1	22	0.4	10.3	64	0.01
KL30-01	785.1	788.4	0.81	8100	0.59	1.8	99	12	6	5	1	11	0.01	5.3	47	0.01
KL30-01	788.4	791.5	0.73	7300	0.34	2.6	590	67	8	31	1	12	0.01	6.0	50	0.01
KL30-01	791.5	794.5	0.84	8400	0.34	3.5	560	67	6	18	1	14	0.01	7.7	36	0.01
KL30-01	794.5	797.5	0.99	9900	0.9	3.5	123	9	7	13	1	16	0.01	6.8	31	0.01
KL30-01	797.5	799.3	0.66	6600	0.66	2.3	130	8	3	2	2	14	0.01	5.5	38	0.01
KL30-01	799.3	801	0.64	6400	0.84	2.5	91	8	51	19	1	16	0.01	5.8	41	0.01
KL30-01	801	804	0.63	6300	0.83	2	680	73	10	16	3	8	0.01	5.3	28	0.01
KL30-01	804	807	0.451	4510	0.75	1.2	570	37	16	45	2	7	0.01	3.8	29	0.01
KL30-01	807	810	1.2	12000	1.4	2.2	119	7	8	14	2	10	0.01	5.5	34	0.01
KL30-01	810	813	0.52	5200	0.51	1.5	126	16	5	15	1	8	0.01	4.0	20	0.01
KL30-01	813	816	0.39	3900	0.36	1.2	85	8	7	44	0.01	10	0.01	3.4	37	0.01
KL30-01	816	819	0.37	3700	0.22	1.3	178	17	4	28	0.01	6	0.01	2.8	15	0.01
KL30-01	819	822	1	10000	0.86	2.4	189	7	3	15	1	14	0.01	5.8	26	0.01
KL30-01	822	825	0.93	9300	0.69	1.5	470	48	14	3	0.01	13	0.2	6.4	23	0.01
KL30-01	825	828	0.75	7500	0.64	1.3	1440	54	16	2	0.01	14	0.01	7.5	22	0.01
KL30-01	828	831	0.75	7500	0.59	1.9	1180	115	29	3	1	15	0.01	6.5	25	0.01
KL30-01	831	834	0.494	4940	0.12	2.5	380	170	36	25	8	10	0.2	9.4	39	0.01
KL30-01	834	837	0.56	5600	0.19	2.8	1960	410	31	35	2	10	0.2	8.5	35	0.01
KL30-01	837	840	0.36	3600	0.06	1.9	1120	200	9	10	1	7	0.01	5.0	29	0.01
KL30-02	0	3	0.0006	6	0.01	0.1	28	18	7	2	0.01	1	0.5	1.6	19	0.01
KL30-02	3	6	0.0006	6	0.01	0.1	42	15	11	2	0.01	1	0.5	1.0	25	0.01
KL30-02	6	9	0.0007	7	0.01	0.1	51	40	12	3	0.01	2	0.7	1.7	22	0.01
KL30-02	9	12	0.0009	9	0.01	0.1	66	86	14	2	0.01	2	1	1.4	26	0.01
KL30-02	12	15	0.0005	5	0.01	0.1	78	51	9	2	0.01	3	0.8	0.8	22	0.01
KL30-02	15	18	0.001	10	0.01	1.4	228	700	8	1	0.01	2	3.3	1.0	22	0.01
KL30-02	18	21	0.001	10	0.01	1.1	175	356	15	1	1	1	1.5	3.1	24	0.01
KL30-02	21	24	0.0021	21	0.02	1	197	198	9	1	0.01	1	1.5	1.4	23	0.01
KL30-02	24	27	0.0008	8	0.01	0.1	31	56	8	1	0.01	1	0.7	0.7	22	0.01
KL30-02	27	30	0.0009	9	0.01	1.2	109	262	17	2	2	1	1.3	2.4	26	0.01
KL30-02	30	33	0.002	20	0.07	6.3	280	2100	19	3	1	1	5.6	8.2	27	0.01
KL30-02	33	36	0.0015	15	0.02	0.1	21	112	17	4	1	1	1.4	3.9	34	0.01
KL30-02	36	39	0.005	50	0.01	0.1	73	120	12	3	0.01	1	1.7	1.3	35	0.01
KL30-02	39	42	0.004	40	0.01	0.1	29	47	8	3	0.01	1	0.9	1.3	23	0.01
KL30-02	42	45	0.0008	8	0.01	0.1	127	261	5	2	0.01	1	0.9	1.3	15	0.01
KL30-02	45	48	0.0006	6	0.01	0.1	70	58	7	1	0.01	2	0.7	1.2	24	0.01
KL30-02	48	51	0.0007	7	0.01	0.1	87	137	9	1	0.01	1	1.2	2.3	28	0.01
KL30-02	51	54	0.0019	19	0.02	1	419	550	31	4	0.01	3	3	1.5	41	0.01
KL30-02	54	57	0.0134	134	0.06	2.2	630	750	47	4	0.01	3	5.1	1.4	85	0.01
KL30-02	57	58.8	0.0134	134	0.04	1.8	161	810	40	6	0.01	4	3.3	1.8	135	0.01
KL30-02	58.8	60.5	0.0062	62	0.05	0.8	61	79	23	11	1	8	1.3	2.5	75	0.01
KL30-02	60.5	63	0.061	610	0.1	25.8	680	16500	220	55	38	15	25	34.3	98	0.01
KL30-02	63	67.5	0.134	1340	0.33	97	383	13800	490	305	132	62	19.5	184.0	34	0.01
KL30-02	67.5	70.5	0.39	3900	0.56	293	49500	16500	890	12	510	8	23	220.0	115	0.01
KL30-02	70.5	73.5	0.0066	66	0.15	5.4	400	2200	35	4	5	1	2.8	6.8	37	0.01
KL30-02	73.5	76.5	0.0017	17	0.02	1.2	90	312	39	9	0.01	1	4.4	4.1	30	0.01
KL30-02	76.5	79.5	0.0042	42	0.11	2.6	319	135	36	7	3	3	3.3	2.5	116	0.01
KL30-02	79.5	81.3	0.0079	79	0.07	0.1	114	71	20	5	1	3	1.1	0.6	20	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL30-02	81.3	83.8	0.011		110	0.06	0.5	119	56	29	6	0.01	1	1.4	0.7	26	0.01
KL30-02	83.8	85.5	0.0124		124	0.09	0.8	232	89	21	7	0.01	2	1.9	1.3	27	0.01
KL30-02	85.5	88.5	0.007		70	0.02	0.1	141	58	9	5	0.01	2	0.6	0.5	18	0.01
KL30-02	88.5	92	0.0069		69	0.01	0.1	41	60	3	4	0.01	1	0.01	0.0	20	0.01
KL30-02	92	95.1	0.0044		44	0.01	0.1	34	87	3	4	0.01	1	0.01	0.5	12	0.01
KL30-02	95.1	97.5	0.0056		56	0.03	0.7	32	153	6	3	0.01	1	0.01	0.5	13	0.01
KL30-02	97.5	100.5	0.0051		51	0.03	0.6	23	73	5	7	0.01	1	0.01	0.0	12	0.01
KL30-02	100.5	103.2	0.0085		85	0.06	3.8	440	940	9	8	1	1	2.2	1.7	18	0.01
KL30-02	103.2	106	0.0078		78	0.09	0.1	30	70	4	4	0.01	1	0.7	1.6	24	0.01
KL30-02	106	109	0.001		10	0.04	0.1	33	61	4	4	0.01	1	0.6	0.0	13	0.01
KL30-02	109	111.8	0.0033		33	0.03	0.1	11	37	5	2	0.01	1	0.01	1.0	10	0.01
KL30-02	111.8	115	0.001		10	0.05	0.1	26	104	4	3	0.01	1	1.2	1.2	24	0.01
KL30-02	115	117	0.0007		7	0.22	3	88	810	8	2	1	1	6.4	1.4	27	0.01
KL30-02	117	120	0.0057		57	0.13	1.4	266	1150	5	5	0.01	1	1.8	1.7	23	0.01
KL30-02	120	123	0.0055		55	0.15	2.7	273	2400	10	5	1	1	4.5	2.5	22	0.01
KL30-02	123	126	0.008		80	0.07	9.2	2300	8000	19	2	0.01	1	13.8	1.8	24	0.01
KL30-02	126	129	0.0077		77	0.05	1.6	75	216	9	10	0.01	1	3.1	1.9	24	0.01
KL30-02	129	132	0.0015		15	0.04	1.6	118	1000	6	3	0.01	1	1.9	6.1	21	0.01
KL30-02	132	134.8	0.0025		25	0.04	1.4	203	810	9	2	0.01	1	1.2	2.2	25	0.01
KL30-02	134.8	137.5	0.0008		8	0.03	0.6	61	160	5	1	0.01	1	2.3	1.5	27	0.01
KL30-02	137.5	139.5	0.0032		32	0.08	4	560	1740	13	4	4	1	3.8	4.7	28	0.01
KL30-02	139.5	142.1	0.0063		63	0.07	8.7	1960	460	15	3	0.01	1	5	1.6	25	0.34
KL30-02	142.1	145	0.0053		53	0.05	1.2	155	430	15	1	0.01	1	1.7	2.0	23	0.01
KL30-02	145	147.2	0.0008		8	0.08	1	64	213	10	3	0.01	1	2.4	1.1	31	0.01
KL30-02	147.2	149.5	0.0062		62	0.07	3.8	1650	2300	16	5	0.01	1	4.4	5.8	33	0.01
KL30-02	149.5	152.4	0.0034		34	0.03	2.9	730	1830	7	6	0.01	1	3.9	3.2	27	0.01
KL30-02	152.4	154.5	0.0032		32	0.03	2.2	213	1730	6	6	0.01	1	3.6	2.4	25	0.01
KL30-02	154.5	156	0.0037		37	0.04	4.7	348	3450	8	4	0.01	1	5.1	2.1	18	0.01
KL30-02	156	156.9	0.24		2400	0.3	578	11500	465000	480	9	1	1	490	67.5	50	0.46
KL30-02	156.9	159	0.121		1210	0.27	132	12100	83600	260	14	0.01	1	125	9.3	17	0.42
KL30-02	159	161.6	0.0031		31	0.05	2.1	660	1210	12	4	0.01	1	2.1	1.1	12	0.01
KL30-02	161.6	164.5	0.0068		68	0.1	2	600	1460	11	11	1	1	2.5	2.8	12	0.01
KL30-02	164.5	167	0.0083		83	0.04	2.4	800	1880	15	7	0.01	1	3.2	1.7	10	0.01
KL30-02	167	169.8	0.0072		72	0.03	1.4	248	1020	6	10	0.01	1	1.3	1.4	13	0.01
KL30-02	169.8	173.7	0.0105		105	0.04	3.8	3000	3600	12	7	0.01	1	4.6	7.3	13	0.01
KL30-02	173.7	176.7	0.0275		275	0.03	15.3	7300	10800	30	23	1	1	14.7	22.4	13	0.01
KL30-02	176.7	178.6	0.0253		253	0.05	16	8400	13700	21	34	1	1	18	8.8	10	0.01
KL30-02	178.6	181.5	0.0058		58	0.04	4.6	3500	3300	8	4	0.01	1	4.5	3.0	18	0.01
KL30-02	181.5	184.5	0.0104		104	0.05	6.4	2800	1750	33	7	4	1	4.7	7.2	13	0.01
KL30-02	184.5	187.5	0.006		60	0.03	4.1	610	1230	20	6	4	1	3.7	4.3	20	0.01
KL30-02	187.5	190.5	0.0154		154	0.05	5.1	2300	1350	53	13	2	1	4.5	4.3	16	0.01
KL30-02	190.5	192	0.014		140	0.04	8.1	2400	1330	34	15	7	1	5.2	5.2	17	0.01
KL30-02	192	195	0.039		390	0.07	17.9	4100	3900	140	11	30	2	13.8	8.5	21	0.01
KL30-02	195	198	0.0235		235	0.08	4.7	3900	2500	50	16	5	3	5.2	5.8	17	0.01
KL30-02	198	201	0.058		580	0.11	3.3	2400	890	110	7	6	2	4.9	6.1	13	0.01
KL30-02	201	204	0.0274		274	0.08	3.5	2900	990	55	6	7	2	3.8	6.0	13	0.01
KL30-02	204	207	0.0168		168	0.07	3	1460	1860	21	9	5	1	2.1	4.2	12	0.01
KL30-02	207	210	0.24		2400	0.57	10.9	7200	10800	79	8	40	1	8.4	10.4	36	0.01
KL30-02	210	212	0.413		4130	0.51	18	4450	2400	68	26	112	16	3.1	34.3	42	0.01
KL30-02	212	214.5	0.67		6700	1.71	8.9	9100	810	220	13	110	2	2.6	52.5	90	0.43
KL30-02	214.5	217.5	0.79		7900	1.7	5.6	1070	540	200	4	80	3	2.8	100.0	187	0.21
KL30-02	217.5	220.5	0.57		5700	0.62	3.3	460	113	78	10	18	42	2.4	59.0	210	0.18
KL30-02	220.5	223.5	1.04		10400	0.72	8.5	490	86	90	129	20	71	1.4	79.5	206	0.32
KL30-02	223.5	226	1.92		19200	1.08	12.8	265	810	100	230	21	78	2.1	55.0	216	0.88
KL30-02	226	228	1.05		10500	0.38	7.7	317	1750	82	136	9	72	7.8	75.0	266	0.42
KL30-02	228	231	1.32		13200	0.28	3.7	101	57	35	1625	4	15	0.6	18.9	476	0.01
KL30-02	231	234	0.427		4270	0.69	3.1	140	53	130	590	8	15	1.2	24.3	299	0.01
KL30-02	234	237	0.57		5700	0.61	7	265	175	62	32	40	11	6.5	12.8	145	0.01
KL30-02	237	240	0.71		7100	0.61	6.7	327	136	93	88	4	28	6.5	14.3	262	0.01
KL30-02	240	243	0.71		7100	0.6	6	312	127	87	78	3	28	5.8	12.5	254	0.25
KL30-02	243	246	1.47		14700	1.01	12.1	276	143	96	98	10	36	5.6	10.3	177	0.18
KL30-02	246	249	1.67		16700	1.03	8.5	174	76	54	78	4	52	3.2	15.5	185	0.14
KL30-02	249	252	1.3		13000	0.9	10	111	40	62	258	9	56	1.9	14.3	179	0.15

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL30-02	252	255	1.18	11800	0.84	7.4	86	23	55	60	4	20	1.9	14.0	191	0.33
KL30-02	255	257.5	0.89	8900	0.65	8	2300	2100	50	78	5	27	4.1	12.3	204	1.02
KL30-02	257.5	259.5	2.02	20200	1.34	12.1	137	70	38	195	3	53	2.5	12.0	257	0.32
KL30-02	259.5	261.5	1.73	17300	1.37	13.4	269	87	46	195	5	58	3.2	24.0	272	0.39
KL30-02	261.5	264	2.36	23600	2.2	22.8	1120	114	61	9	7	37	2.1	25.0	208	0.82
KL30-02	264	266.5	3.06	30600	1.08	16.8	480	38	94	2	13	26	1.7	25.0	162	0.59
KL30-02	266.5	268.5	1.67	16700	0.73	8.3	246	32	29	3	16	19	1	23.7	156	0.38
KL30-02	268.5	271.5	2.95	29500	0.94	12.4	119	19	50	6	12	35	4.5	43.0	192	0.57
KL30-02	271.5	274.7	1.78	17800	1.18	4.6	160	37	64	2010	13	64	3.1	45.5	209	0.29
KL30-02	274.7	277.5	2.03	20300	1.24	4.4	118	43	80	1620	14	80	3.5	50.2	200	0.23
KL30-02	277.5	280.5	2.39	23900	1.01	5.8	52	24	44	760	5	44	1.3	51.5	204	0.32
KL30-02	280.5	283.5	1.24	12400	0.54	1.5	281	310	53	1450	5	42	1.4	29.3	171	0.16
KL30-02	283.5	285.5	2.18	21800	0.8	2.8	63	34	85	320	3	50	2.1	35.0	152	0.5
KL30-02	285.5	288.5	2.33	23300	1.13	4.3	83	26	37	143	3	38	0.8	34.0	146	0.27
KL30-02	288.5	291	5.69	56900	1.34	10.6	86	32	52	8	7	48	1.6	32.6	104	1.12
KL30-02	291	294	0.5	5000	0.59	2.1	67	37	100	428	13	40	1.9	36.0	157	0.01
KL30-02	294	297	7.83	78300	1.44	14	60	34	86	3	4	37	1.5	26.3	119	0.85
KL30-02	297	300	3.36	33600	0.96	9.7	59	18	280	21	10	42	1.9	18.5	233	0.52
KL30-02	300	303	2.56	25600	0.76	2.8	56	31	47	20	4	42	0.8	25.5	174	0.3
KL30-02	303	306	1.09	10900	0.93	1.9	160	41	34	125	2	25	0.8	14.5	154	0.17
KL30-02	306	309	0.119	1190	0.18	0.8	40	13	12	187	1	14	0.3	17.5	166	0.01
KL30-02	309	311.5	0.299	2990	0.19	1	19	12	17	272	4	12	0.6	28.3	163	0.01
KL30-02	311.5	314	0.085	850	0.14	0.1	16	11	17	390	2	10	0.4	27.5	201	0.01
KL30-02	314	316.5	0.052	520	0.15	0.1	24	6	18	256	1	8	0.5	30.2	143	0.01
KL30-02	316.5	319.5	0.245	2450	0.25	1	22	9	41	327	8	22	1.6	25.7	211	0.01
KL30-02	319.5	322.5	3.63	36300	1.04	6.3	56	22	240	10	9	50	2.2	48.0	212	0.01
KL30-02	322.5	325.5	2.33	23300	1.32	6.5	30	16	91	13	16	43	3.1	28.3	301	0.01
KL30-02	325.5	328.5	1.73	17300	0.99	5.7	291	268	43	36	11	31	1.9	22.5	163	0.01
KL30-02	328.5	331.5	1.85	18500	0.93	9.4	67	57	55	6	26	51	1.5	35.5	201	0.01
KL30-02	331.5	334.5	1.89	18900	1.29	10.8	31	18	130	7	18	31	2.2	26.5	101	0.01
KL30-02	334.5	337.5	1.69	16900	1.35	9.7	89	72	220	426	19	49	3.3	30.5	116	0.01
KL30-02	337.5	340.5	0.9	9000	0.85	7.4	354	127	170	32	12	56	1.9	21.8	161	0.15
KL30-02	340.5	343.5	0.95	9500	1.33	11.8	362	283	390	44	7	34	4.6	15.5	186	0.2
KL30-02	343.5	346.5	1.39	13900	1.84	16.7	1040	720	360	42	10	45	4.5	25.0	180	0.21
KL30-02	346.5	349.5	0.54	5400	1.09	6.6	324	178	87	78	7	22	2.1	14.1	255	0.01
KL30-02	349.5	352.5	0.85	8500	0.59	5.1	71	47	43	38	8	23	3.1	17.5	180	0.01
KL30-02	352.5	355.5	0.25	2500	0.36	2.9	54	28	17	56	3	11	0.8	10.3	233	0.01
KL30-02	355.5	358.2	0.268	2680	1.1	3.6	83	32	18	79	3	13	0.2	9.0	184	0.15
KL30-02	358.2	361.5	2.37	23700	2.08	13.5	660	236	120	10	5	61	2.7	17.5	211	0.01
KL30-02	361.5	364.5	2.85	28500	1.88	17.6	3400	1550	160	4	6	58	4.9	21.5	314	0.01
KL30-02	364.5	367.5	1.26	12600	1.08	10.7	1870	3750	190	12	11	51	8	19.8	158	0.01
KL30-02	367.5	370.5	1.63	16300	1.65	14.3	2300	3200	220	16	7	35	8.9	23.5	190	0.01
KL30-02	370.5	373	0.3	3000	0.61	3.3	1930	2060	180	16	4	6	6.5	17.5	84	0.01
KL30-02	373	375.2	0.67	6700	1.55	3.5	1000	790	170	16	2	20	2.5	17.8	122	0.01
KL30-02	375.2	378	0.68	6800	1.45	9.3	2050	2250	340	3	6	9	7.8	13.8	97	0.68
KL30-02	378	381	0.178	1780	0.62	2.2	440	346	200	43	4	20	7.4	32.2	155	0.1
KL30-02	381	384	0.263	2630	0.7	1.6	78	53	130	54	2	4	3.8	18.8	96	0.01
KL30-02	384	387	0.061	610	0.91	0.8	78	60	200	32	5	3	3.7	21.3	120	0.01
KL30-02	387	390	0.064	640	1.02	0.7	54	32	300	215	11	2	3.5	11.0	84	0.01
KL30-02	390	392	0.0071	71	0.11	0.1	36	15	82	34	1	2	1.4	2.3	61	0.01
KL30-02	392	393.5	0.0054	54	0.47	0.1	41	32	310	85	1	3	4.4	2.3	66	0.1
KL30-02	393.5	396	0.0044	44	1.19	0.1	64	33	450	357	1	3	6.6	6.0	51	0.35
KL30-02	396	399	0.0087	87	0.72	0.7	78	35	280	39	1	2	3.7	1.8	60	0.18
KL30-02	399	402	0.003	30	0.19	0.1	91	32	170	26	0.01	1	1.5	2.0	57	0.01
KL30-02	402	405	0.0152	152	0.16	0.6	148	67	130	10	1	2	1.6	2.5	62	0.15
KL30-02	405	408	0.169	1690	1.31	2.2	295	64	430	21	4	6	9.9	6.0	70	0.77
KL30-02	408	411	0.64	6400	1.72	8.6	250	115	480	22	12	8	15	6.5	50	0.34
KL30-02	411	415	0.38	3800	2.14	23.2	7400	5900	310	212	80	14	15.5	25.0	62	0.65
KL30-02	415	418.2	0.96	9600	1.71	13.3	291	253	350	77	134	12	11.1	11.5	63	0.25
KL30-02	418.2	420.4	0.38	3800	1.01	29.9	13200	22000	200	52	92	8	19.7	56.4	76	0.17
KL30-02	420.4	423	0.0181	181	0.35	4.1	3600	3230	93	9	1	4	7.1	15.1	36	0.12
KL30-02	423	426	0.0175	175	0.68	9.4	1240	2000	140	16	6	5	17.3	12.5	47	0.55
KL30-02	426	429	0.087	870	0.92	10.7	4000	2100	240	26	7	4	58	20.5	41	1.04

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL30-02	429	432	0.28		2800	2	51	37300	23700	500	30	2	6	162	43.8	43	1.84
KL30-02	432	435	0.0075		75	0.28	0.1	201	278	85	7	1	5	3.8	0.7	30	0.01
KL30-02	435	438	0.0201		201	0.39	2.2	600	670	130	17	5	4	5.7	0.7	28	0.17
KL30-02	438	441	0.0155		155	0.34	1.9	1460	860	120	31	11	5	3.6	11.0	50	0.01
KL30-02	441	444	0.0038		38	0.1	0.5	349	146	68	4	0.01	2	1.7	0.7	23	0.01
KL30-02	444	447	0.056		560	0.63	17.5	22500	33500	120	13	3	4	12.7	526.0	56	0.13
KL30-02	447	450	0.049		490	0.28	1.4	214	213	110	11	1	5	3.1	3.0	29	0.01
KL30-02	450	453	0.0074		74	0.16	1.5	540	970	110	6	2	4	3.3	3.0	25	0.01
KL30-02	453	454.3	0.0397		397	0.24	1.5	530	450	110	22	5	4	3.1	3.7	23	0.11
KL30-02	454.3	456	0.0103		103	0.06	0.6	46	43	20	3	0.01	2	1	0.0	25	0.01
KL30-02	456	459	0.0166		166	0.08	0.1	70	28	27	8	0.01	4	1	1.5	25	0.01
KL30-03	0	3	0.0025		25	0.01	0.1	41	16	6	3	0.01	1	0.4	0.5	25	0.01
KL30-03	3	6	0.0035		35	0.01	0.1	55	22	8	4	0.01	1	0.4	0.7	34	0.01
KL30-03	6	9	0.0045		45	0.01	0.1	79	34	11	4	0.01	1	0.7	0.8	35	0.01
KL30-03	9	12	0.0041		41	0.01	0.1	104	51	9	3	0.01	1	0.4	1.2	29	0.01
KL30-03	12	15	0.0035		35	0.01	0.7	127	49	11	4	0.01	1	1.1	2.1	31	0.01
KL30-03	15	18	0.0027		27	0.01	0.1	218	162	8	3	0.01	1	0.7	0.8	27	0.01
KL30-03	18	21	0.0045		45	0.01	0.1	115	133	7	1	0.01	1	0.5	0.7	26	0.01
KL30-03	21	24	0.0021		21	0.01	0.1	57	74	8	1	0.01	1	0.3	0.7	26	0.01
KL30-03	24	27	0.004		40	0.01	0.1	38	51	6	1	0.01	1	0.3	0.7	26	0.01
KL30-03	27	30	0.0035		35	0.01	0.1	52	76	9	2	0.01	1	0.3	0.0	31	0.01
KL30-03	30	33	0.002		20	0.04	0.1	50	99	12	1	0.01	1	0.7	1.2	32	0.01
KL30-03	33	36	0.0018		18	0.05	0.7	42	155	5	1	0.01	1	1.5	0.8	28	0.01
KL30-03	36	39	0.0027		27	0.05	0.1	33	58	15	1	0.01	1	0.7	2.1	32	0.01
KL30-03	39	42	0.003		30	0.09	0.1	42	90	20	3	0.01	1	0.9	2.7	32	0.01
KL30-03	42	45	0.0025		25	0.02	0.1	49	27	14	1	0.01	1	0.3	1.0	26	0.01
KL30-03	45	48	0.0021		21	0.01	0.1	20	17	6	1	0.01	1	0.01	1.0	32	0.01
KL30-03	48	51	0.0024		24	0.01	0.1	38	33	8	3	0.01	1	0.5	0.7	38	0.01
KL30-03	51	54	0.0019		19	0.01	0.1	17	15	5	1	0.01	1	0.2	0.6	32	0.01
KL30-03	54	57	0.0018		18	0.04	0.1	30	92	7	1	0.01	1	0.5	0.8	28	0.01
KL30-03	57	60.5	0.0027		27	0.05	0.1	44	36	14	1	0.01	1	0.5	0.6	28	0.01
KL30-03	60.5	63	0.0164		164	0.08	1.2	960	330	51	1	4	6	0.7	2.3	136	0.01
KL30-03	63	66	0.0085		85	0.06	2.2	428	670	37	2	2	6	2.8	1.1	189	0.1
KL30-03	66	67.6	0.0052		52	0.06	1.5	250	274	30	1	2	5	2.1	1.8	193	0.01
KL30-03	67.6	69.9	0.0051		51	0.1	1.3	94	106	36	2	0.01	6	1.2	2.6	106	0.01
KL30-03	69.9	75.2	0.213		2130	0.23	68	1190	4560	420	6	10	1	600	9.6	15	0.21
KL30-03	75.2	79.5	0.0085		85	0.05	3.5	780	940	53	4	1	1	10	7.6	59	0.1
KL30-03	79.5	82.5	0.0054		54	0.02	1.3	670	590	13	1	1	1	3.3	3.5	278	0.01
KL30-03	82.5	85.5	0.0036		36	0.02	1.4	470	730	7	3	0.01	1	0.8	8.7	61	0.01
KL30-03	85.5	87.5	0.021		210	0.21	2	168	161	15	19	1	1	5.3	3.6	80	0.01
KL30-03	87.5	90	0.101		1010	0.1	38	5900	4000	340	7	2	1	89	9.7	206	0.23
KL30-03	90	94.5	0.0045		45	0.05	1.2	253	229	10	6	0.01	1	2.3	0.0	363	0.1
KL30-03	94.5	99	0.008		80	0.09	1.2	374	318	18	6	3	1	4.5	0.8	268	0.01
KL30-03	99	102.1	0.0168		168	0.04	1.1	168	156	7	5	1	1	0.8	0.0	219	0.01
KL30-03	102.1	105	0.0238		238	0.04	0.7	105	95	7	5	2	1	0.5	0.7	196	0.01
KL30-03	105	108	0.0011		11	0.02	0.1	28	64	2	4	0.01	1	0.3	0.0	294	0.01
KL30-03	108	111	0.0007		7	0.01	0.1	16	24	2	6	0.01	1	0.2	0.0	143	0.01
KL30-03	111	114	0.0008		8	0.03	0.5	59	66	5	7	0.01	1	0.4	0.0	72	0.01
KL30-03	114	117	0.001		10	0.05	1.1	74	306	5	5	0.01	1	0.9	0.0	158	0.01
KL30-03	117	120	0.0004		4	0.09	1	33	343	4	5	0.01	1	1.7	0.9	51	0.13
KL30-03	120	122.5	0.0022		22	0.21	1.3	67	201	24	5	0.01	1	3.9	3.2	87	0.01
KL30-03	122.5	125.5	0.002		20	0.13	5.2	74	2750	22	10	1	1	11.9	1.7	38	0.1
KL30-03	125.5	130.5	0.006		60	0.21	12.9	1260	9800	22	9	1	1	17.3	3.3	32	0.15
KL30-03	130.5	133.5	0.0016		16	0.05	3.7	530	2970	4	7	0.01	1	7.2	3.5	76	0.01
KL30-03	133.5	137.3	0.0004		4	0.03	0.1	51	54	1	5	0.01	1	0.5	0.0	30	0.01
KL30-03	137.3	141	0.0005		5	0.06	1.2	321	70	8	3	0.01	1	2.8	1.3	35	0.01
KL30-03	141	145	0.0004		4	0.03	0.1	68	110	2	3	0.01	1	0.3	1.6	34	0.01
KL30-03	145	148.5	0.0009		9	0.03	0.1	201	145	3	3	0.01	1	0.9	1.9	36	0.1
KL30-03	148.5	151.9	0.0013		13	0.05	0.9	148	164	23	1	2	4	1.1	3.2	40	0.1
KL30-03	151.9	155.5	0.002		20	0.11	2.8	730	2440	22	3	1	1	2.9	8.5	30	0.1
KL30-03	155.5	158.5	0.0004		4	0.05	0.1	71	84	3	2	0.01	1	1.1	1.3	41	0.1
KL30-03	158.5	162.2	0.0006		6	0.08	0.6	139	170	6	2	0.01	1	1.1	1.6	40	0.1
KL30-03	162.2	167.9	0.0011		11	0.14	0.7	76	229	13	10	0.01	1	2.4	1.1	44	0.13

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL30-03	167.9	175.3	0.0094	94	0.08	7.3	4360	3290	16	117	10	1	3.4	8.1	20	0.13
KL30-03	175.3	178.5	0.0034	34	0.03	1.8	610	1780	4	16	0.01	1	2.6	3.2	23	0.1
KL30-03	178.5	181.5	0.0089	89	0.07	1.9	630	670	21	38	0.01	1	2.5	2.0	24	0.01
KL30-03	181.5	184.1	0.0292	292	0.07	3.8	1640	1240	53	36	6	1	5.8	9.5	23	0.01
KL30-03	184.1	187.1	0.043	430	0.08	4.8	1480	1070	140	41	5	1	15.3	4.7	26	0.21
KL30-03	187.1	190.2	0.036	360	0.38	7.8	2660	3760	88	34	6	1	15	5.5	24	0.21
KL30-03	190.2	193.4	0.0394	394	0.21	8.6	3440	2260	96	36	16	1	14.1	8.2	27	0.2
KL30-03	193.4	196.5	0.0109	109	0.01	0.1	61	20	2	3	0.01	15	0.01	0.0	24	0.01
KL30-03	196.5	199.5	0.0284	284	0.21	8.1	2730	1910	57	10	16	1	8.2	8.0	26	0.21
KL30-03	199.5	202.5	0.0148	148	0.11	2.8	2810	1280	29	13	5	1	2.6	4.0	24	0.12
KL30-03	202.5	205.5	0.087	870	0.38	12.1	8300	9200	360	58	23	1	34	16.8	23	0.27
KL30-03	205.5	209	0.098	980	0.4	3.1	1260	790	250	23	9	1	18.8	20.0	32	0.13
KL30-03	209	211.5	0.076	760	0.26	3.2	670	400	38	22	15	1	2.1	12.2	32	0.14
KL30-03	211.5	214.5	0.318	3180	1.21	8	700	230	180	16	35	6	2.7	30.0	99	0.1
KL30-03	214.5	217.5	0.74	7400	4.25	23.4	710	1530	170	42	162	6	3.1	40.5	73	0.01
KL30-03	217.5	220.5	1.24	12400	2.71	10	1310	327	72	53	15	26	3.6	70.0	227	1.03
KL30-03	220.5	223.5	1.31	13100	1.84	6.5	328	107	19	60	17	42	1.5	47.0	100	0.01
KL30-03	223.5	226.5	1.31	13100	1.68	8	680	239	24	63	4	27	1.3	31.5	86	0.01
KL30-03	226.5	228	2.41	24100	4.44	13.7	490	221	47	17	3	43	2.1	25.5	112	0.37
KL30-03	228	230.1	0.93	9300	1.24	7.2	173	167	58	32	14	53	17.5	45.6	224	0.56
KL30-03	230.1	232.5	0.377	3770	0.38	3.3	59	67	78	98	10	54	5.3	90.0	140	0.14
KL30-03	232.5	235.5	0.242	2420	0.28	2.3	84	69	41	2440	6	34	2	45.0	350	0.01
KL30-03	235.5	238.5	0.435	4350	0.41	3.2	75	85	45	116	6	38	2.2	38.2	355	0.12
KL30-03	238.5	241.5	1.31	13100	1.26	6.7	150	142	66	211	4	47	4.8	41.0	286	0.43
KL30-03	241.5	244.5	1.14	11400	1.14	5.7	217	187	67	29	5	36	6.2	25.0	146	0.29
KL30-03	244.5	247.5	2.92	29200	0.56	7.5	67	68	59	17	4	36	2.3	27.0	299	0.52
KL30-03	247.5	250.5	2.33	23300	0.97	7.4	127	117	110	72	5	40	2.9	51.0	305	0.37
KL30-03	250.5	253.5	2.47	24700	0.99	4.2	52	55	34	19	3	51	2.6	43.0	249	0.97
KL30-03	253.5	256.5	1.6	16000	0.81	3.2	46	28	68	156	4	41	2.5	44.0	299	0.39
KL30-03	256.5	259.5	0.142	1420	0.51	1.2	31	37	60	149	5	59	1.7	42.4	328	0.01
KL30-03	259.5	262.5	1.29	12900	0.71	3.5	73	41	47	520	3	75	1.2	35.5	329	0.32
KL30-03	262.5	265.5	2.54	25400	1.5	5.2	178	137	60	117	1	90	2.2	4.0	244	0.48
KL30-03	265.5	268.5	4.01	40100	2.22	10.1	298	105	65	107	1	84	7	20.0	197	0.36
KL30-03	268.5	271.5	1.93	19300	1.73	4.2	97	57	102	283	3	88	2.4	34.0	315	0.17
KL30-03	271.5	274.4	1.23	12300	0.86	1.6	36	24	30	203	2	75	1.3	47.0	230	0.12
KL30-03	274.4	277.5	1.91	19100	0.68	2.7	33	17	30	171	5	73	0.8	34.5	207	0.15
KL30-03	277.5	280.5	1.67	16700	0.57	3.9	28	20	86	615	4	57	2.5	30.0	296	0.01
KL30-03	280.5	284.5	0.86	8600	0.52	1.5	38	30	40	860	2	43	1.6	23.0	257	0.11
KL30-03	284.5	286.5	0.75	7500	0.44	1.1	34	37	35	640	2	63	1	39.0	184	0.1
KL30-03	286.5	289.5	1.59	15900	0.75	3.2	45	24	75	193	4	44	2.4	29.0	261	0.1
KL30-03	289.5	292.5	1.46	14600	0.84	2.4	30	19	41	510	6	43	1.3	36.0	338	0.01
KL30-03	292.5	295.5	0.81	8100	0.86	2.6	269	104	110	160	15	100	2.7	44.0	250	0.11
KL30-03	295.5	298.5	1.42	14200	0.94	3.7	28	19	56	108	6	82	3.5	49.0	256	0.1
KL30-03	298.5	300	2.61	26100	2.4	5.3	50	41	0.01	107	0.01	1	1.6	70.0	207	0.1
KL30-03	300	303	0.68	6800	1.12	4.3	680	270	0.01	92	0.01	1	10.1	43.0	304	0.1
KL30-03	303	306	0.442	4420	0.44	1.4	33	46	0.01	103	0.01	1	8.3	49.0	253	0.01
KL30-03	306	309	1.78	17800	1.29	7.6	48	43	0.01	26	0.01	1	13.6	43.5	205	0.01
KL30-03	309	312.2	2.93	29300	2.63	16	365	85	0.01	12	0.01	1	13.5	37.0	191	0.14
KL30-03	312.2	315	2.81	28100	3.75	17	1800	156	0.01	270	0.01	1	2.6	30.0	30	0.01
KL30-03	315	317.9	2.58	25800	2.87	15.5	2300	1020	0.01	48	0.01	1	4.4	45.0	173	0.01
KL30-03	317.9	321	0.94	9400	1.19	7.6	305	160	0.01	43	0.01	1	5.4	36.3	52	0.01
KL30-03	321	323.7	0.56	5600	1.88	10.3	3890	1200	0.01	39	0.01	1	5.7	23.0	152	0.01
KL30-03	323.7	327	1.13	11300	3.1	46	27700	10400	0.01	210	0.01	1	10.5	57.0	148	0.18
KL30-03	327	330	1.66	16600	2.04	43	18000	5400	0.01	180	0.01	1	16.7	66.8	94	0.33
KL30-03	330	333	2.16	21600	2.24	83	52300	15000	0.01	296	0.01	1	19.6	97.0	227	0.45
KL30-03	333	336	1.79	17900	2.48	61	43200	9100	0.01	430	0.01	1	34	52.8	351	0.52
KL30-03	336	339	0.62	6200	1.73	31.2	25500	10500	0.01	102	0.01	1	18.8	30.5	75	0.19
KL30-03	339	342	1.05	10500	1.8	32	36000	8900	0.01	760	0.01	1	12.2	23.8	56	0.4
KL30-03	342	345	1.15	11500	2.76	36.5	61400	6800	0.01	1690	0.01	1	31	73.0	198	0.55
KL30-03	345	348	3.2	32000	2.12	45	29500	5700	0.01	104	0.01	1	24	105.0	157	0.13
KL30-03	348	350.5	2.51	25100	4.02	69	97800	19000	0.01	215	0.01	1	34	185.0	72	0.64
KL30-03	350.5	353.5	0.141	1410	0.99	17.9	9700	6000	0.01	136	0.01	1	32	52.0	85	0.32
KL30-03	353.5	357	0.086	860	0.23	5.7	4460	1300	0.01	41	0.01	1	6.5	12.7	25	0.14

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL30-03	357	360	0.1	1000	0.17	7.9	3890	1870	0.01	42	0.01	1	4.6	19.3	23	0.13
KL30-03	360	363	0.087	870	0.57	6.6	2880	1140	0.01	61	0.01	1	14.1	9.5	53	0.23
KL30-03	363	366	0.29	2900	0.62	33.8	17100	12300	0.01	440	0.01	1	30	48.0	43	0.18
KL30-03	366	369	0.145	1450	0.6	20.7	7600	4300	0.01	140	0.01	1	40	28.7	64	0.27
KL30-03	369	372	0.126	1260	0.46	14.2	5200	3600	0.01	110	0.01	1	24	9.6	46	0.22
KL30-03	372	375	0.092	920	0.47	24.5	16900	10800	0.01	40	0.01	1	20	83.0	35	0.24
KL30-03	375	378	0.49	4900	0.29	17.3	8200	2800	0.01	238	0.01	1	9.5	17.2	38	0.01
KL30-03	378	381	0.42	4200	0.94	66	16700	22000	0.01	163	0.01	1	172	26.2	45	0.82
KL30-03	381	384	0.135	1350	0.53	24.9	6700	3000	0.01	110	0.01	1	74	15.7	31	0.36
KL30-03	384	387	0.48	4800	0.52	24.3	13400	8200	0.01	340	0.01	1	32	53.0	26	0.45
KL30-03	387	390	0.125	1250	0.47	9.4	4880	2780	0.01	110	0.01	1	17.5	19.5	27	0.24
KL30-03	390	393	0.082	820	0.76	19	5160	7500	0.01	103	0.01	1	38	22.5	44	0.29
KL30-03	393	396	0.052	520	0.64	4.3	2110	1000	0.01	41	0.01	1	8.3	11.0	42	0.3
KL30-03	396	399	0.37	3700	2.23	11.3	6300	3800	0.01	138	0.01	1	17.8	26.7	30	0.55
KL30-03	399	402	0.071	710	0.44	5.4	14800	5700	0.01	7	0.01	1	7.5	29.5	32	0.25
KL30-03	402	405	0.28	2800	0.48	2.9	930	356	0.01	21	0.01	1	7.7	5.8	26	0.1
KL30-03	405	408	0.299	2990	1.26	5.4	2990	1430	0.01	48	0.01	1	13	17.5	22	0.4
KL30-03	408	411	0.186	1860	0.19	2.6	1580	660	0.01	22	0.01	1	4.9	8.0	16	0.01
KL30-03	411	414	0.0297	297	0.13	1.2	430	165	0.01	12	0.01	1	2.3	3.2	17	0.14
KL30-03	414	417	0.131	1310	0.17	2.1	800	172	0.01	50	0.01	1	3.7	7.5	11	0.17
KL30-03	417	420	0.071	710	0.48	2.3	1410	600	0.01	26	0.01	1	6.9	7.1	30	0.14
KL30-03	420	423	0.059	590	0.17	2.2	2410	1090	0.01	66	0.01	1	3.5	23.0	21	0.01
KL30-03	423	426	0.145	1450	0.21	2.8	2790	407	0.01	16	0.01	1	3.2	5.1	23	0.1
KL30-03	426	429	0.0283	283	0.15	1.3	740	376	0.01	17	0.01	1	2.5	4.9	30	0.01
KL30-03	429	432	0.0324	324	0.13	1.1	470	283	0.01	18	0.01	1	3.5	2.8	29	0.01
KL30-03	432	435	0.0218	218	0.09	0.8	293	126	0.01	10	0.01	1	1.5	8.0	26	0.01
KL30-03	435	438	0.072	720	0.12	5.6	2560	2440	0.01	48	0.01	1	5.7	1.2	24	0.01
KL30-03	438	441.2	0.0087	87	0.03	0.1	136	65	0.01	4	0.01	1	2.1	0.6	25	0.01
KL30-03	441.2	444	0.0021	21	0.02	0.1	25	8	0.01	1	0.01	1	0.5	0.6	24	0.01
KL30-03	444	447	0.0022	22	0.01	0.1	17	9	0.01	1	0.01	1	0.5	0.8	24	0.01
KL30-03	447	450	0.0142	142	0.04	0.1	45	10	0.01	2	0.01	1	1	1.7	31	0.01
KL30-03	450	453	0.098	980	0.09	1.2	78	12	0.01	10	0.01	1	1.1	1.1	27	0.01
KL30-03	453	456	0.089	890	0.07	0.8	89	10	0.01	5	0.01	1	0.5	0.6	24	0.01
KL30-03	456	459	0.0361	361	0.04	0.1	73	8	0.01	3	0.01	1	0.5	1.1	28	0.01
KL30-03	459	462	0.0158	158	0.04	0.1	165	84	0.01	6	0.01	1	2.5	0.6	30	0.01
KL30-03	462	465	0.0283	283	0.09	0.1	60	9	0.01	4	0.01	1	0.8	0.0	28	0.01
KL30-03	465	468	0.0057	57	0.04	0.1	47	11	0.01	6	0.01	1	1	0.0	32	0.12
KL30-03	468	471	0.0047	47	0.02	0.1	38	8	0.01	3	0.01	1	0.6	0.0	31	0.1
KL30-03	471	474	0.0036	36	0.08	0.1	41	6	0.01	2	0.01	1	1.2	0.0	33	0.16
KL30-03	474	477	0.0048	48	0.08	0.1	56	6	0.01	11	0.01	1	1.9	0.0	36	0.23
KL30-03	477	480	0.0297	297	0.04	0.1	78	7	0.01	15	0.01	1	1.1	0.6	36	0.15
KL30-03	480	483	0.072	720	0.06	0.1	115	11	0.01	5	0.01	1	1.1	1.2	27	0.14
KL30-03	483	486	0.063	630	0.04	0.1	98	12	0.01	2	0.01	1	0.8	0.9	24	0.1
KL30-04	0	3	0.0059	59	0.01	0.1	35	25	9	3	0.01	1	0.01	1.0	22	0.01
KL30-04	3	6	0.008	80	0.01	0.1	45	17	6	3	0.01	2	0.5	1.2	22	0.01
KL30-04	6	9	0.005	50	0.01	0.1	56	24	11	4	0.01	3	0.9	0.5	31	0.01
KL30-04	9	12	0.0057	57	0.01	0.1	66	61	12	4	0.01	3	1.1	0.7	30	0.01
KL30-04	12	15	0.007	70	0.01	1.4	2110	480	12	2	0.01	3	1.4	2.5	35	0.01
KL30-04	15	18	0.0075	75	0.01	0.6	164	48	9	3	0.01	3	0.4	1.0	26	0.01
KL30-04	18	21	0.0029	29	0.01	0.6	53	25	11	3	0.01	3	0.7	1.2	24	0.01
KL30-04	21	24	0.0029	29	0.01	1.5	1770	820	14	3	0.01	2	1.6	1.0	25	0.01
KL30-04	24	27	0.0037	37	0.01	0.6	131	106	9	2	0.01	2	0.9	1.5	25	0.01
KL30-04	27	30	0.0061	61	0.01	1.3	182	225	8	2	0.01	1	1.8	1.8	26	0.01
KL30-04	30	33	0.0041	41	0.01	0.1	40	28	11	2	0.01	1	0.01	1.0	23	0.01
KL30-04	33	36	0.0031	31	0.01	0.1	27	16	5	1	0.01	1	0.01	0.8	27	0.01
KL30-04	36	39	0.005	50	0.01	0.1	28	18	8	3	0.01	1	0.4	1.0	28	0.01
KL30-04	39	42	0.0074	74	0.04	0.9	107	105	13	1	0.01	1	10.6	0.7	24	0.01
KL30-04	42	45	0.007	70	0.04	0.1	37	23	6	2	0.01	1	0.5	1.2	21	0.01
KL30-04	45	48	0.0153	153	0.18	1	401	83	31	1	0.01	1	9.1	2.5	20	0.01
KL30-04	48	51	0.0041	41	0.01	0.1	24	25	13	1	0.01	1	1.1	2.0	26	0.01
KL30-04	51	54	0.0032	32	0.01	0.1	34	27	10	1	0.01	2	0.3	0.8	33	0.01
KL30-04	54	57	0.0046	46	0.01	0.1	36	19	3	1	0.01	3	0.2	0.9	32	0.01
KL30-04	57	60	0.006	60	0.01	0.1	18	13	5	1	0.01	1	0.01	1.2	30	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL30-04	60	63	0.006		60	0.01	0.1	20	10	6	2	0.01	1	0.01	0.8	30	0.01
KL30-04	63	66	0.004		40	0.01	0.1	17	9	3	4	0.01	1	0.01	0.7	29	0.01
KL30-04	66	69	0.0044		44	0.01	0.1	26	14	5	1	0.01	1	0.3	1.6	26	0.01
KL30-04	69	72	0.003		30	0.01	0.1	34	18	6	1	0.01	1	0.01	0.5	20	0.01
KL30-04	72	75	0.0033		33	0.01	0.1	28	10	3	1	0.01	1	0.01	0.6	35	0.01
KL30-04	75	78	0.005		50	0.01	0.1	48	14	4	1	0.01	1	0.2	0.5	63	0.01
KL30-04	78	81	0.0049		49	0.01	0.1	50	21	4	1	0.01	1	0.01	0.7	54	0.01
KL30-04	81	84.1	0.0107		107	0.01	0.1	51	24	16	1	0.01	2	1.4	0.0	56	0.01
KL30-04	84.1	87	0.0257		257	0.04	0.5	89	106	16	4	0.01	4	2.2	1.2	76	0.01
KL30-04	87	90	0.0133		133	0.14	1.2	277	236	35	3	0.01	7	3.6	4.5	44	0.01
KL30-04	90	93	0.0246		246	0.09	8.8	5100	6300	64	6	1	2	15.4	10.8	11	0.01
KL30-04	93	96	0.0047		47	0.08	1.2	750	840	8	18	0.01	1	2.2	1.5	12	0.01
KL30-04	96	98.2	0.0065		65	0.06	1.1	540	560	12	5	0.01	1	6.1	1.2	22	0.01
KL30-04	98.2	102	0.0283		283	0.16	5.3	820	860	61	3	8	1	7.7	5.9	38	0.01
KL30-04	102	105	0.0239		239	1.21	8.7	2100	3600	90	13	8	1	14.5	5.6	45	0.13
KL30-04	105	108.1	0.0102		102	0.56	1.8	88	267	27	14	0.01	1	6.2	1.2	27	0.01
KL30-04	108.1	112	0.0165		165	0.11	1.2	430	235	20	8	1	1	3.1	6.9	28	0.01
KL30-04	112	114.8	0.0057		57	0.05	1.6	550	670	10	2	0.01	1	2.1	0.8	16	0.01
KL30-04	114.8	118.3	0.0098		98	0.01	0.6	80	185	5	6	0.01	1	0.5	0.7	15	0.01
KL30-04	118.3	121	0.0094		94	0.01	0.5	53	92	4	8	0.01	1	0.4	0.6	17	0.01
KL30-04	121	123	0.0108		108	0.01	1	137	155	5	5	0.01	1	1.1	0.7	22	0.01
KL30-04	123	126	0.0066		66	0.01	0.1	21	34	2	3	0.01	1	0.01	0.0	19	0.01
KL30-04	126	129	0.0098		98	0.01	0.1	21	28	2	4	0.01	1	1.2	0.0	17	0.01
KL30-04	129	132	0.0076		76	0.02	0.1	49	74	2	6	0.01	1	0.6	0.0	14	0.01
KL30-04	132	135	0.0088		88	0.06	1.3	730	520	3	7	0.01	1	1.7	1.6	18	0.01
KL30-04	135	138	0.0089		89	0.09	1.1	64	80	8	12	0.01	1	1.2	1.0	20	0.01
KL30-04	138	141	0.0144		144	0.12	5.4	720	1530	23	14	2	2	5.6	3.0	32	0.01
KL30-04	141	144	0.0079		79	0.21	1.4	243	520	10	8	0.01	1	4.3	1.7	27	0.01
KL30-04	144	147	0.0205		205	0.34	12.6	2770	3400	26	8	21	2	11.8	16.7	49	0.15
KL30-04	147	150	0.0328		328	0.86	16.7	5700	5600	180	36	14	3	26	11.5	60	0.5
KL30-04	150	153	0.0073		73	0.31	3.7	660	1220	19	12	3	2	6.1	3.5	32	0.01
KL30-04	153	154.6	0.0058		58	0.23	3.4	1300	1570	24	14	2	2	6.5	4.2	19	0.01
KL30-04	154.6	157.6	0.0019		19	0.08	1.1	198	320	7	6	0.01	2	3.7	1.6	23	0.01
KL30-04	157.6	160.2	0.0022		22	0.06	1	137	227	5	6	1	2	3.1	1.6	30	0.01
KL30-04	160.2	163.3	0.0049		49	0.06	6.6	357	1660	13	10	10	3	2.8	5.5	26	0.01
KL30-04	163.3	166.6	0.0075		75	0.44	2.6	500	358	34	30	3	2	4.8	6.0	29	0.01
KL30-04	166.6	169.5	0.004		40	0.11	0.8	116	107	23	45	2	2	5.4	2.7	30	0.01
KL30-04	169.5	172.9	0.0035		35	0.1	1	76	95	26	34	1	6	2.3	2.5	24	0.01
KL30-04	172.9	175	0.0032		32	0.05	2.2	241	120	5	13	1	1	2.2	1.3	21	0.11
KL30-04	175	177	0.0019		19	0.04	1.1	62	131	3	24	1	1	1.1	1.6	32	0.01
KL30-04	177	180	0.0025		25	0.07	1.6	123	480	24	17	4	2	1.7	3.5	30	0.01
KL30-04	180	182.3	0.0018		18	0.04	1.1	70	430	7	8	1	2	1.4	1.5	29	0.01
KL30-04	182.3	186.5	0.0199		199	0.1	6.1	129	630	48	27	5	2	24	2.0	31	0.01
KL30-04	186.5	189.5	0.0124		124	0.16	5.6	1280	1570	53	38	13	2	14	2.7	38	0.19
KL30-04	189.5	192	0.0032		32	0.07	9.1	215	2140	8	40	18	2	2.6	3.1	30	0.01
KL30-04	192	195.4	0.0042		42	0.05	3.2	370	1400	9	26	5	2	4	4.2	30	0.01
KL30-04	195.4	198.7	0.0044		44	0.04	1.6	570	640	9	25	2	3	1.8	3.4	19	0.01
KL30-04	198.7	201.3	0.0112		112	0.06	3.4	1500	1220	19	63	7	2	4.6	5.5	14	0.01
KL30-04	201.3	204	0.0279		279	0.18	2.8	1020	960	100	54	3	3	14.5	7.7	22	0.11
KL30-04	204	207.5	0.0187		187	0.09	2.5	890	1180	27	47	2	2	8.3	6.7	14	0.01
KL30-04	207.5	210	0.075		750	0.26	13	5300	2200	210	126	22	3	17	7.3	18	0.32
KL30-04	210	213	0.0242		242	0.13	2.2	880	940	51	85	3	2	8.4	6.5	20	0.01
KL30-04	213	216	0.0192		192	0.07	2.1	800	910	31	108	3	3	7.6	4.5	18	0.01
KL30-04	216	219	0.046		460	0.14	7.2	2750	3000	210	135	12	2	12	6.6	15	0.11
KL30-04	219	222	0.33		3300	1.15	27.4	10500	5000	470	433	56	7	22	34.9	33	0.88
KL30-04	222	225	0.32		3200	1.28	18.1	11800	3800	540	103	44	6	32	30.0	28	0.85
KL30-04	225	228	0.11		1100	0.44	15.4	5900	2900	330	197	24	3	26	7.6	19	0.42
KL30-04	228	231	0.37		3700	0.69	32.8	20000	7000	840	186	57	7	75	36.2	28	1.05
KL30-04	231	234	1.02		10200	3.2	15.8	7000	520	540	95	138	17	10	45.7	45	1.02
KL30-04	234	237	0.66		6600	2.27	8.5	2170	930	110	106	41	12	5	34.0	45	0.26
KL30-04	237	239.5	1		10000	2.85	5	1000	279	150	56	36	13	5.7	39.5	146	0.5
KL30-04	239.5	243	0.25		2500	0.4	2.4	244	151	240	45	14	17	6.6	105.0	254	0.2
KL30-04	243	246	0.168		1680	0.46	2.6	173	132	220	138	10	46	10.2	43.0	184	0.38

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL30-04	246	248.5	0.27		2700	0.38	2.3	224	143	430	227	8	38	22	45.8	226	0.19
KL30-04	248.5	251.5	0.27		2700	0.33	2.6	124	71	500	698	4	38	34	20.0	103	0.21
KL30-04	251.5	254.5	0.2		2000	0.37	1.8	134	48	200	336	5	65	12.7	42.0	80	0.1
KL30-04	254.5	258	0.56		5600	0.35	1.6	56	39	450	307	3	63	20	41.6	287	0.01
KL30-04	258	261	0.55		5500	0.23	1.8	47	38	600	206	2	73	20	46.4	289	0.01
KL30-04	261	264	0.198		1980	0.28	1.2	62	51	310	449	3	89	16	46.5	331	0.01
KL30-04	264	267	0.66		6600	0.47	1.5	60	62	180	280	3	109	6	45.5	216	0.01
KL30-04	267	270	1.39		13900	0.43	2	36	32	170	347	2	126	7.8	58.0	193	0.01
KL30-04	270	273	0.33		3300	0.39	0.7	37	30	220	528	4	120	11.2	49.5	238	0.01
KL30-04	273	276	2.05		20500	0.83	6.7	92	52	300	215	7	106	12.6	30.5	268	0.01
KL30-04	276	277.6	2.78		27800	1.76	6.6	407	88	600	151	8	151	20	56.5	328	0.12
KL30-04	277.6	280.6	0.71		7100	1.24	2.5	130	73	610	70	8	74	18.7	48.3	259	0.01
KL30-04	280.6	283.6	0.3		3000	1.49	3.6	378	295	650	31	47	58	24	65.8	316	0.1
KL30-04	283.6	287	0.58		5800	0.92	1.7	90	56	1210	67	14	47	55	61.3	260	0.1
KL30-04	287	290	0.31		3100	1.16	1.5	64	45	880	206	14	26	36	60.8	308	0.01
KL30-04	290	292.5	0.545		5450	2	4.1	97	72	990	145	106	8	30	47.3	285	0.01
KL30-04	292.5	295	0.43		4300	1.73	22.4	36000	4100	820	223	77	11	16.4	41.0	139	0.1
KL30-04	295	297	0.485		4850	0.71	18	6100	3400	160	118	19	26	16.4	23.5	61	0.01
KL30-04	297	300	0.655		6550	0.32	26	19300	4600	150	195	28	28	5.5	45.0	57	0.01
KL30-04	300	303	0.059		590	0.14	2.4	1840	550	52	56	7	11	1.4	9.0	41	0.01
KL30-04	303	306	0.091		910	0.12	24	13100	4050	36	116	73	7	2.2	37.1	38	0.01
KL30-04	306	309	0.46		4600	0.87	23	19500	8700	180	209	32	26	11.2	22.4	54	0.1
KL30-04	309	312	0.183		1830	1.63	27	30700	20900	360	244	45	8	25	18.7	34	0.32
KL30-04	312	314	0.049		490	0.21	1.7	920	560	67	41	11	2	2.6	6.0	26	0.01
KL30-04	314	318	0.054		540	0.43	16	10200	11600	69	42	23	1	14.3	15.2	32	0.42
KL30-04	318	321	0.0186		186	0.18	4	2330	2400	30	39	11	1	3.2	11.5	22	0.01
KL30-04	321	323.5	0.017		170	0.08	2.4	800	450	23	46	8	1	1.1	4.0	29	0.01
KL30-04	323.5	326.25	0.0386		386	0.1	8.3	5500	1100	36	343	227	1	6.2	16.2	28	0.01
KL30-04	326.25	330	0.0225		225	0.08	3.4	2200	1080	41	37	11	2	2.2	9.3	26	0.01
KL30-04	330	333	0.0376		376	0.34	5.1	3800	2700	84	67	8	5	9.1	21.7	38	0.01
KL30-04	333	336	0.0321		321	0.22	4.4	2240	2500	62	82	8	2	6.9	28.6	36	0.01
KL30-04	336	339	0.051		510	0.23	5.4	2470	3700	140	99	13	3	9.5	97.0	39	0.01
KL30-04	339	342	0.0323		323	0.22	3.9	2810	1830	130	92	9	4	7.6	25.0	41	0.01
KL30-04	342	345	0.0365		365	0.2	11.1	8200	6900	71	292	8	4	15.9	35.9	44	0.01
KL30-04	345	347	0.033		330	0.15	6.9	6000	4000	110	111	13	5	7	39.0	48	0.01
KL30-04	347	350	0.082		820	0.3	12.2	5700	7200	220	136	29	8	13.9	92.0	58	0.01
KL30-04	350	352.7	0.071		710	0.3	13.5	10100	6650	160	96	16	7	12.2	53.5	39	0.01
KL30-04	352.7	355	0.018		180	0.05	0.6	205	290	9	16	3	1	0.7	10.5	25	0.01
KL30-04	355	358	0.121		1210	0.2	5.2	3500	1800	38	94	35	6	4.2	23.0	40	0.01
KL30-04	358	360	0.0395		395	0.09	2.8	1170	930	16	51	21	4	1.2	15.7	30	0.01
KL30-04	360	363	0.0287		287	0.11	2.6	1520	1180	27	62	45	2	1.7	16.2	36	0.01
KL30-04	363	366	0.3		3000	0.16	3.5	1790	480	47	251	53	12	4.8	10.2	48	0.01
KL30-04	366	369	0.0363		363	0.07	2.8	4000	3000	29	63	6	4	3.3	10.7	33	0.01
KL30-04	369	372	0.06		600	0.24	8.3	7400	4550	100	125	33	10	11.4	98.8	36	0.1
KL30-04	372	375	0.048		480	0.34	10	8900	4900	120	130	22	11	14.4	78.8	34	0.01
KL30-04	375	378	0.049		490	0.34	14.4	13700	8300	140	250	36	10	14.5	97.5	43	0.1
KL30-04	378	381	0.0271		271	0.15	6.5	5100	2700	72	85	30	9	6.9	37.5	26	0.01
KL30-04	381	384	0.0139		139	0.08	4	2850	2100	42	64	7	7	5	13.0	22	0.01
KL30-04	384	387	0.0359		359	0.18	9.7	3950	2400	59	176	68	5	10.6	30.5	18	0.01
KL30-04	387	390	0.0217		217	0.2	7.5	5700	2900	130	53	14	6	5.6	32.0	27	0.01
KL30-04	390	393	0.066		660	0.11	8.2	2890	5700	58	28	2	3	15	12.7	32	0.01
KL30-04	393	396	0.103		1030	0.15	11.5	10100	7400	60	67	18	8	14.5	36.0	28	0.01
KL30-04	396	399	0.055		550	0.08	2.1	357	1050	45	32	3	3	6.3	10.1	21	0.01
KL30-04	399	402	0.0385		385	0.05	2	395	930	30	30	3	4	3.2	5.2	28	0.01
KL30-04	402	405	0.0238		238	0.15	4	1210	1630	22	46	2	3	3.6	25.0	31	0.01
KL30-04	405	408	0.0163		163	0.04	1.3	399	259	17	83	2	3	4.1	3.5	21	0.01
KL30-04	408	411	0.0236		236	0.06	2.2	363	640	33	58	1	3	5.7	13.7	21	0.01
KL30-04	411	414	0.0166		166	0.06	1.7	610	560	21	41	2	3	2.4	7.4	19	0.01
KL30-04	414	417	0.0214		214	0.05	1.7	740	630	10	10	1	3	2.9	7.0	24	0.01
KL30-04	417	420	0.371		3710	0.25	10.7	2980	3200	52	160	14	7	19.7	10.8	31	0.01
KL30-04	420	423	0.0249		249	0.08	1.5	630	332	22	15	5	3	3.4	2.0	27	0.01
KL30-04	423	426	0.0099		99	0.1	1.2	620	280	25	4	0.01	3	2.3	3.7	22	0.01
KL30-04	426	429	0.0196		196	0.55	1.6	198	134	35	1	0.01	3	3.7	7.5	37	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL30-04	429	432	0.317		3170	0.17	7	1920	2300	33	81	8	4	15.5	7.1	24	0.01
KL30-04	432	435	0.0134		134	0.05	1.3	235	55	17	15	1	4	1.9	8.7	21	0.01
KL30-04	435	439	0.0124		124	0.07	0.1	221	134	17	4	0.01	2	1.1	2.0	16	0.01
KL30-05	0	3	0.0021		21	0.01	0.1	82	103	6	4	0.01	1	0.7	0.6	13	0.01
KL30-05	3	5.5	0.0026		26	0.01	0.1	51	43	12	2	0.01	1	0.8	0.0	31	0.01
KL30-05	5.5	8.5	0.0033		33	0.01	0.1	163	112	17	5	0.01	1	1.7	1.0	28	0.01
KL30-05	8.5	11.5	0.0028		28	0.01	0.1	248	65	8	3	0.01	1	0.7	2.2	40	0.01
KL30-05	11.5	14.5	0.0017		17	0.01	0.6	67	38	14	4	0.01	1	0.9	0.6	37	0.01
KL30-05	14.5	17.5	0.0012		12	0.01	0.5	93	68	18	3	0.01	1	0.9	0.0	34	0.01
KL30-05	17.5	20.5	0.0016		16	0.01	1	188	341	15	1	0.01	1	2	0.8	31	0.01
KL30-05	20.5	23.5	0.0032		32	0.01	1.4	286	610	31	3	1	1	2.4	0.0	33	0.01
KL30-05	23.5	26.5	0.0038		38	0.02	0.9	179	304	36	4	0.01	1	2.1	0.7	31	0.01
KL30-05	26.5	29.5	0.0039		39	0.03	1.8	387	860	51	13	0.01	2	3.1	2.1	29	0.01
KL30-05	29.5	32.5	0.0015		15	0.14	3.9	212	1280	45	33	1	2	4.6	4.0	35	0.01
KL30-05	32.5	35.5	0.0016		16	0.24	17.8	281	6850	17	3	2	1	16.6	12.0	30	0.01
KL30-05	35.5	38.5	0.0012		12	0.18	2.5	268	600	16	3	0.01	1	4.1	3.0	24	0.01
KL30-05	38.5	41.5	0.004		40	0.17	2.8	256	1280	30	10	1	1	12.5	5.2	56	0.01
KL30-05	41.5	44.5	0.0018		18	0.03	1.4	274	1070	21	8	0.01	1	4	1.6	43	0.01
KL30-05	44.5	47.5	0.0078		78	0.01	4.5	550	1430	46	48	6	1	3.8	4.8	32	0.01
KL30-05	47.5	50.5	0.0063		63	0.05	10.5	2190	12000	26	57	3	1	8	3.3	23	0.01
KL30-05	50.5	53.5	0.0121		121	0.03	8.9	1210	3710	40	91	1	1	4.3	6.0	26	0.01
KL30-05	53.5	56.5	0.113		1130	0.07	8.1	700	1660	46	92	4	6	4.6	13.8	91	0.01
KL30-05	56.5	59.5	0.122		1220	0.03	6	490	630	46	36	4	2	3.8	1.7	86	0.01
KL30-05	59.5	61	0.0134		134	0.07	2.6	280	820	27	20	1	3	3.4	2.8	138	0.01
KL30-05	61	63	0.0168		168	0.03	2	500	620	35	13	1	5	5.5	2.8	166	0.01
KL30-05	63	64.9	0.0277		277	0.05	4	710	790	35	57	1	9	4	3.3	117	0.01
KL30-05	64.9	65.9	6.12		61200	0.82	203	14200	15500	1350	25	113	9	50	32.0	107	0.4
KL30-05	65.9	68.5	0.325		3250	0.26	30	5600	3140	350	45	28	3	8.6	21.4	32	0.01
KL30-05	68.5	70	0.0215		215	0.16	10.4	1330	3800	66	15	9	1	3.2	4.8	122	0.01
KL30-05	70	73	0.0133		133	0.09	2.8	106	335	34	44	0.01	1	3.8	1.8	118	0.01
KL30-05	73	76	0.07		700	0.14	8	480	3680	160	15	8	5	14	3.6	106	0.01
KL30-05	76	79	0.0295		295	0.13	14.1	610	1700	110	5	21	4	3.8	6.7	195	0.01
KL30-05	79	81.5	0.0061		61	0.1	2	278	236	32	6	1	3	1.4	2.4	146	0.01
KL30-05	81.5	84.5	0.0028		28	0.08	1.3	96	264	32	8	0.01	4	2.3	2.3	150	0.01
KL30-05	84.5	86.5	0.0046		46	0.12	1.7	144	126	29	6	1	3	1.8	2.2	220	0.01
KL30-05	86.5	89.5	0.021		210	0.11	2.7	223	163	62	9	1	2	3.7	2.5	208	0.01
KL30-05	89.5	93	0.0016		16	0.09	2.6	128	269	30	7	0.01	1	3.5	0.6	134	0.01
KL30-05	93	95.5	0.0016		16	0.05	2	166	304	24	8	0.01	1	2.3	0.5	130	0.01
KL30-05	95.5	98.5	0.0018		18	0.64	5.1	315	430	57	13	2	1	5.6	1.7	107	0.01
KL30-05	98.5	101.1	0.0012		12	0.08	2.5	164	350	40	9	0.01	1	2.8	0.0	97	0.01
KL30-05	101.1	104.3	0.0091		91	1.15	29	2500	20000	110	15	6	1	27.5	6.0	80	0.01
KL30-05	104.3	107.5	0.0054		54	0.14	8.3	3600	6650	8	6	0.01	2	9.1	4.3	32	0.01
KL30-05	107.5	110.2	0.0023		23	0.06	2.7	870	1730	9	6	0.01	1	3.2	2.1	19	0.01
KL30-05	110.2	112.9	0.016		160	0.05	8.2	2500	6700	6	9	1	1	6.4	2.7	19	0.01
KL30-05	112.9	115.7	0.0015		15	0.04	5.8	2500	3900	4	4	0.01	1	6.1	3.8	19	0.01
KL30-05	115.7	118	0.0032		32	0.04	2	450	1120	2	5	0.01	1	1.9	1.3	20	0.01
KL30-05	118	120.7	0.0008		8	0.03	1.4	178	610	7	2	0.01	1	1.5	0.8	17	0.01
KL30-05	120.7	123.1	0.0063		63	0.04	1.9	390	1180	17	30	0.01	1	1.9	2.0	21	0.01
KL30-05	123.1	125.6	0.0022		22	0.02	1.2	560	580	7	17	0.01	1	1.8	1.3	22	0.01
KL30-05	125.6	128.5	0.0102		102	0.02	4.3	810	1150	29	4	5	1	2.1	2.0	20	0.01
KL30-05	128.5	131.4	0.0079		79	0.07	8.6	4600	2800	28	3	5	1	4.6	2.7	21	0.15
KL30-05	131.4	134.5	0.0055		55	0.05	6.6	2500	3690	14	6	3	1	6.9	2.8	34	0.01
KL30-05	134.5	137.5	0.0012		12	0.41	4.5	450	680	22	5	0.01	1	3.9	2.2	29	0.01
KL30-05	137.5	140.2	0.0015		15	0.09	1.4	127	194	11	4	0.01	1	1	0.6	25	0.01
KL30-05	140.2	142.8	0.0011		11	0.13	4.6	1130	1300	9	3	0.01	1	3.2	3.2	27	0.01
KL30-05	142.8	145.8	0.0042		42	0.02	4.2	830	1890	5	2	2	1	3.1	2.1	22	0.01
KL30-05	145.8	148.8	0.0022		22	0.01	2.9	750	1300	7	10	0.01	1	2.8	1.9	14	0.01
KL30-05	148.8	150.3	0.0014		14	0.01	1.9	268	740	5	4	0.01	1	1.8	1.8	15	0.01
KL30-05	150.3	153.3	0.002		20	0.02	2	670	880	7	10	0.01	1	1.3	1.4	12	0.01
KL30-05	153.3	156	0.0095		95	0.01	2.8	1020	1440	6	10	0.01	1	4.5	1.5	15	0.01
KL30-05	156	157.5	0.0165		165	0.01	1.6	240	440	4	7	0.01	1	2	1.2	13	0.01
KL30-05	157.5	160	0.0062		62	0.02	3.4	780	890	9	6	0.01	1	3.3	1.9	12	0.01
KL30-05	160	163	0.0018		18	0.02	2.3	323	930	3	4	0.01	1	2.3	1.3	10	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL30-05	163	166	0.0028		28	0.05	2.9	1200	710	7	4	0.01	1	3.9	1.2	12	0.01
KL30-05	166	168.9	0.0083		83	0.06	10.8	1840	4990	12	24	0.01	1	11.7	3.1	15	0.01
KL30-05	168.9	171.7	0.052		520	0.15	124	67900	91700	70	45	2	1	140	15.5	20	0.21
KL30-05	171.7	174.7	0.0122		122	0.08	42	9400	29700	21	5	2	1	40	8.1	16	0.01
KL30-05	174.7	177.1	0.0051		51	0.2	15.6	5300	7400	19	2	0.01	1	13.9	4.5	14	0.23
KL30-05	177.1	179.3	0.0027		27	0.29	4	1130	980	15	1	0.01	1	3.1	3.2	16	0.01
KL30-05	179.3	181.7	0.0057		57	0.28	9.8	8900	6300	21	7	3	1	8.8	3.4	12	0.56
KL30-05	181.7	184	0.0151		151	0.13	16.9	19600	13100	19	6	1	1	16.7	11.0	14	0.11
KL30-05	184	187	0.0091		91	0.05	3.3	2640	1220	15	4	0.01	1	2	2.5	13	0.01
KL30-05	187	189.7	0.01		100	0.11	5.2	9000	2800	11	36	7	1	6.2	4.1	16	0.25
KL30-05	189.7	192.6	0.0072		72	0.01	1.1	770	610	6	6	0.01	2	1.8	2.0	12	0.01
KL30-05	192.6	195.2	0.0106		106	0.3	5.1	5900	3200	15	6	0.01	1	6.3	3.6	13	0.26
KL30-05	195.2	197.4	0.006		60	0.11	3.6	5400	2020	12	7	1	1	5.3	2.5	12	0.16
KL30-05	197.4	200.1	0.009		90	0.17	3.8	2370	2450	15	8	2	1	3.7	4.5	16	0.01
KL30-05	200.1	202	0.0078		78	0.12	2.1	2700	2070	9	5	1	1	3	2.9	14	0.01
KL30-05	202	205	0.0069		69	0.12	3.9	3260	3270	13	12	1	2	6.2	6.3	13	0.13
KL30-05	205	208	0.0042		42	0.21	6.3	7100	3800	13	10	1	1	5.1	5.7	12	0.34
KL30-05	208	211	0.0055		55	0.34	3.8	2000	1460	22	9	2	1	5.9	4.5	12	0.01
KL30-05	211	213.3	0.005		50	0.17	2.1	2000	840	9	10	1	1	5.1	4.6	13	0.18
KL30-05	213.3	215.9	0.0143		143	0.15	1.5	3600	1250	18	9	2	1	3.9	2.6	13	0.14
KL30-05	215.9	218.5	0.013		130	0.18	4.6	6000	1890	15	54	12	3	4.5	5.6	15	0.24
KL30-05	218.5	221.5	0.0097		97	0.16	4.1	2340	1300	60	23	7	2	5.8	5.5	12	0.01
KL30-05	221.5	224.2	0.012		120	0.11	2.6	2340	1510	28	9	1	2	4.4	4.8	14	0.01
KL30-05	224.2	226.2	0.0233		233	0.16	2.4	2090	1070	57	32	6	2	3.1	4.5	19	0.01
KL30-05	226.2	228.8	0.058		580	0.16	3.2	690	760	30	30	10	3	1.8	6.5	15	0.01
KL30-05	228.8	231	0.364		3640	1.03	12.4	338	284	64	580	340	12	2.9	19.5	37	0.01
KL30-05	231	233.5	0.0314		314	0.21	2.5	790	450	41	1210	26	4	3	4.3	35	0.01
KL30-05	233.5	236.5	0.0293		293	0.12	1.2	67	45	40	1400	26	3	0.4	2.8	21	0.01
KL30-05	236.5	239.5	0.0354		354	0.18	3.6	1830	229	69	1240	61	6	3.1	4.3	27	0.01
KL30-05	239.5	241.8	0.36		3600	0.76	18.5	8400	470	83	670	203	29	3.4	14.5	21	0.01
KL30-05	241.8	244	0.75		7500	1.09	34	7550	1440	1050	125	89	20	60	19.3	45	0.01
KL30-05	244	247	0.303		3030	0.49	8.1	800	185	64	1440	16	14	5.1	14.3	25	0.01
KL30-05	247	250	0.357		3570	1.12	7.6	430	135	49	970	6	18	1.7	17.3	21	0.01
KL30-05	250	253	0.064		640	0.3	1.8	86	56	41	1065	44	4	0.5	6.3	25	0.01
KL30-05	253	256	0.292		2920	0.56	4	141	41	19	690	4	8	0.7	6.8	23	0.01
KL30-05	256	259	0.259		2590	0.64	4.8	760	138	56	92	9	9	8.9	8.0	30	0.01
KL30-05	259	262	0.418		4180	0.87	5.8	125	41	68	61	8	14	3	8.5	31	0.11
KL30-05	262	265	0.76		7600	2.47	11.1	2350	56	68	10	90	34	3.6	21.8	41	0.01
KL30-05	265	268	0.8		8000	1.37	9.2	730	70	73	118	45	41	3.3	21.6	66	0.1
KL30-05	268	271	0.325		3250	0.88	3.3	510	450	22	365	84	14	2.2	14.1	146	0.01
KL30-05	271	274	0.64		6400	2.6	7.8	10300	148	33	99	177	40	0.7	17.3	31	0.01
KL30-05	274	277	0.114		1140	0.37	3.8	7200	940	89	11	16	12	21.5	15.3	16	1
KL30-05	277	279	0.39		3900	0.71	8	10100	850	590	28	26	32	27	19.8	37	1.66
KL30-05	279	281.1	0.19		1900	0.34	2	5400	45	310	20	14	23	17.4	16.0	30	1.13
KL30-05	281.1	284.5	0.92		9200	2	5.4	13800	70	68	5	28	80	5.5	31.3	73	0.58
KL30-05	284.5	287.5	1.2		12000	1.88	4.2	1180	95	25	72	9	142	4.8	32.5	59	0.01
KL30-05	287.5	290.5	1.78		17800	1.65	5	3950	136	27	28	4	33	3.2	14.8	44	0.01
KL30-05	290.5	293.5	3.69		36900	2.88	11.8	550	124	41	68	3	60	4.9	58.0	141	0.13
KL30-05	293.5	296.5	3.36		33600	2.58	7.2	276	208	12	79	1	65	3.5	25.3	61	0.01
KL30-05	296.5	299.5	3.99		39900	3.25	7.8	460	64	4	72	1	58	0.8	20.5	38	0.01
KL30-05	299.5	302.5	2.56		25600	2.4	5.8	286	62	6	63	2	49	1.5	13.7	50	0.01
KL30-05	302.5	305.5	5.11		51100	4.05	12.2	1070	386	25	54	1	55	4.5	28.0	51	0.01
KL30-05	305.5	308.5	5.02		50200	4.42	8	1190	420	33	84	1	52	5.8	34.0	54	0.01
KL30-05	308.5	311.5	6.07		60700	4.82	14	570	134	54	57	1	67	4.6	19.0	113	0.01
KL30-05	311.5	314.5	3.1		31000	1.16	15.4	2800	640	3600	510	1	48	80	33.0	261	1.2
KL30-05	314.5	316.9	2.1		21000	0.45	5.7	256	98	45	1210	1	43	0.6	17.0	132	0.38
KL30-05	316.9	319	2.32		23200	0.33	6.5	2650	780	830	1280	1	51	26.5	18.0	152	1.57
KL30-05	319	322	2.02		20200	0.85	4.7	670	150	25	389	1	71	0.01	17.5	82	0.37
KL30-05	322	325	2.04		20400	0.93	17.3	3450	980	1120	126	1	98	6.3	17.3	121	1.68
KL30-05	325	328	1.03		10300	0.42	4.2	280	179	240	186	2	43	2.1	10.5	115	0.54
KL30-05	328	331	0.84		8400	0.51	16.4	1370	490	760	170	16	40	9.8	14.0	157	0.8
KL30-05	331	334	0.94		9400	0.41	2.7	520	470	60	231	0.01	32	0.5	11.3	258	0.39
KL30-05	334	337	0.99		9900	0.49	4.8	670	950	400	322	0.01	42	4	17.3	163	0.7

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL30-05	337	340	1.37	13700	0.37	4.1	372	199	600	467	2	48	10.9	13.3	146	0.46
KL30-05	340	341.5	1.89	18900	0.5	6.1	830	324	120	390	1	47	0.5	13.1	126	0.87
KL30-05	341.5	344.5	1.27	12700	0.65	8.6	9000	3750	1890	310	2	38	17.3	16.0	94	5.93
KL30-05	344.5	347.5	1.34	13400	0.34	3.8	3700	430	64	115	0.01	38	0.2	12.1	49	1.51
KL30-05	347.5	350.5	0.94	9400	0.37	1.8	480	215	9	170	0.01	28	0.6	10.3	58	0.01
KL30-05	350.5	353.5	0.88	8800	0.41	1.6	1520	460	210	530	0.01	37	2.4	12.5	108	0.49
KL30-05	353.5	356.5	1.15	11500	0.5	4.4	308	240	250	220	1	28	5.1	9.5	66	0.01
KL30-05	356.5	359.5	1.17	11700	0.76	2.7	172	34	16	179	1	34	0.01	8.8	70	0.01
KL30-05	359.5	362.5	1.04	10400	0.43	2	1430	349	62	371	1	43	0.4	9.8	87	0.12
KL30-05	362.5	365.5	1.22	12200	0.5	1.5	90	17	3	590	0.01	65	0.01	11.3	67	0.01
KL30-05	365.5	368.5	1.54	15400	0.68	2	97	50	5	280	0.01	45	0.4	12.1	90	0.01
KL30-05	368.5	371.5	1.46	14600	0.75	2.4	54	17	8	470	0.01	35	0.01	11.4	53	0.01
KL30-05	371.5	374.5	0.93	9300	0.67	2.5	1140	1310	24	180	0.01	19	0.4	9.7	84	0.01
KL30-05	374.5	377.5	0.82	8200	0.43	1.6	98	402	18	240	1	31	0.4	9.0	61	0.01
KL30-05	377.5	380.5	1.48	14800	0.5	2.3	202	149	5	500	0.01	32	0.01	7.4	77	0.01
KL30-05	380.5	383.5	1.56	15600	0.71	2.3	145	490	3	600	0.01	29	0.3	10.5	128	0.01
KL30-05	383.5	385.5	2.72	27200	1.28	3.1	127	35	3	4000	0.01	45	0.01	13.0	79	0.01
KL30-05	385.5	386.9	0.82	8200	1.13	2.2	227	101	20	430	0.01	10	2.4	8.5	56	0.01
KL30-05	386.9	389.5	3.19	31900	1.06	3.9	145	22	2	980	0.01	41	0.01	15.8	92	0.01
KL30-05	389.5	392.1	3.59	35900	1.2	4.4	157	27	10	1130	0.01	44	0.2	21.0	99	0.01
KL30-05	392.1	394	1.59	15900	0.15	2.5	310	291	19	500	1	11	1.9	10.3	130	0.01
KL30-05	394	397	0.96	9600	0.12	6.3	1840	610	450	392	4	7	3.2	10.8	354	0.3
KL30-05	397	400	1.37	13700	0.25	2.6	1250	308	220	126	2	9	1.1	11.5	271	0.29
KL30-05	400	403	0.9	9000	0.38	1.4	94	32	13	136	1	13	0.3	9.8	190	0.01
KL30-05	403	406	1.32	13200	0.53	3	980	413	46	129	0.01	10	1.7	9.3	250	0.01
KL30-05	406	409	1.46	14600	1.3	2.8	88	45	145	83	1	12	2.3	11.8	316	0.01
KL30-05	409	412	0.91	9100	0.24	2.2	480	125	310	60	2	4	34	8.8	319	0.21
KL30-05	412	414.5	1.05	10500	0.16	1.5	102	27	27	71	1	4	1.5	7.0	170	0.01
KL30-05	414.5	416	0.97	9700	0.23	1.3	111	37	20	76	2	3	5.3	7.3	184	0.01
KL30-05	416	418.5	1.01	10100	0.52	1.4	68	22	2	159	1	3	0.6	8.1	170	0.01
KL30-05	418.5	421	1.64	16400	0.77	2.6	68	35	2	60	1	6	0.4	5.5	194	0.01
KL30-05	421	424	1.51	15100	0.73	1.9	103	34	3	95	1	7	0.2	8.5	99	0.01
KL30-05	424	427	1.01	10100	0.17	1.4	154	51	70	82	1	6	4.5	7.0	134	0.01
KL30-05	427	428.7	0.62	6200	0.14	1	303	93	50	397	0.01	9	1	4.8	254	0.14
KL30-05	428.7	431.3	0.87	8700	0.19	6.9	2900	6310	1510	126	5	12	46	10.7	241	0.9
KL30-05	431.3	434.4	0.85	8500	0.21	2.3	62	34	24	178	0.01	8	0.5	7.6	87	0.01
KL30-05	434.4	437	1.04	10400	0.25	1.7	281	80	60	165	0.01	10	0.8	9.5	253	0.12
KL30-05	437	439.6	0.46	4600	0.12	1.1	323	139	20	107	0.01	5	0.4	5.5	123	0.01
KL30-05	439.6	442.5	0.74	7400	0.14	1.3	415	103	76	93	0.01	6	0.8	5.3	268	0.01
KL30-05	442.5	444	0.88	8800	0.29	1.4	81	23	4	181	0.01	5	0.4	4.0	261	0.01
KL30-05	444	447	1.01	10100	0.22	1.7	186	122	140	172	0.01	8	1.4	6.8	275	0.01
KL30-05	447	450	1.69	16900	0.75	2.7	70	66	6	174	1	9	0.5	9.5	326	0.01
KL30-05	450	453	1.18	11800	0.67	29.5	510	334	1140	183	43	9	35	7.3	305	0.3
KL30-05	453	456	1.32	13200	0.45	6	1250	570	320	160	2	8	4.5	8.5	366	0.32
KL30-05	456	459	1.83	18300	0.52	6.9	530	387	280	232	3	30	3.3	10.0	254	0.19
KL30-05	459	462	1.73	17300	0.46	2.5	620	450	36	271	0.01	30	0.7	13.3	323	0.25
KL30-05	462	465	1.27	12700	0.56	1.8	56	23	5	197	0.01	25	0.6	10.0	317	0.01
KL30-05	465	468	1.45	14500	0.57	3	197	105	43	268	2	24	1	10.0	335	0.01
KL30-05	468	471	1.31	13100	0.52	2	690	291	16	117	0.01	22	0.4	9.5	314	0.01
KL30-05	471	474	1.65	16500	0.64	3	530	500	19	286	0.01	18	0.7	8.3	399	0.01
KL30-05	474	477	1.36	13600	0.29	1.6	300	115	50	357	0.01	13	0.6	7.5	378	0.01
KL30-05	477	480	0.8	8000	0.18	1.8	171	177	390	370	0.01	8	42	7.0	390	0.12
KL30-05	480	483	0.96	9600	0.51	9.5	76	50	320	670	3	8	76	6.5	360	0.48
KL30-05	483	486	0.82	8200	0.21	1.5	112	58	32	480	0.01	9	2.7	7.0	380	0.01
KL30-05	486	489	0.63	6300	0.14	1.2	47	45	18	138	0.01	8	2.9	6.0	117	0.01
KL30-05	489	492	0.513	5130	0.1	0.8	212	274	50	140	0.01	7	2.7	6.3	244	0.15
KL30-05	492	494.1	1.07	10700	0.33	1.9	68	37	5	283	0.01	20	0.3	6.3	106	0.01
KL30-05	494.1	496.2	2.36	23600	1.21	4.2	117	11	1	95	0.01	43	0.01	19.0	33	0.01
KL30-05	496.2	498	1.5	15000	0.48	2.7	109	12	1	250	1	44	0.2	12.0	36	0.01
KL30-05	498	501	1.1	11000	0.35	2.1	125	10	0.01	55	0.01	44	0.01	11.0	51	0.01
KL30-05	501	504	0.77	7700	0.29	1.7	116	9	0.01	205	0.01	36	0.01	6.5	30	0.01
KL30-05	504	507	1.24	12400	0.43	1.8	98	8	0.01	44	0.01	35	0.01	8.5	36	0.01
KL30-05	507	510	1.34	13400	0.53	1.7	137	12	2	45	0.01	35	0.3	7.0	31	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL30-05	510	513	0.45	4500	0.2	0.7	75	9	2	275	0.01	24	0.3	2.3	17	0.01
KL30-05	513	515.2	1.99	19900	0.65	2.4	124	10	0.01	530	0.01	56	0.01	14.2	30	0.01
KL30-05	515.2	518.2	0.72	7200	0.33	1.1	82	12	6	163	0.01	32	0.3	6.0	18	0.01
KL30-05	518.2	521.2	1.51	15100	0.57	2.6	145	10	2	28	0.01	40	0.3	9.0	31	0.01
KL30-05	521.2	524.2	1.33	13300	0.6	2.7	139	15	4	57	0.01	44	3.4	9.5	26	0.01
KL30-05	524.2	527.2	1.76	17600	0.68	3	125	11	1	170	0.01	36	0.01	13.8	11	0.01
KL30-05	527.2	530.2	1.36	13600	0.59	2.2	100	9	4	173	0.01	27	0.2	11.0	25	0.01
KL30-05	530.2	533.2	1.47	14700	0.81	2.4	136	19	12	243	0.01	32	0.2	10.0	46	0.01
KL30-05	533.2	536.2	1.78	17800	0.73	2.3	195	14	2	140	0.01	33	0.01	13.0	29	0.01
KL30-05	536.2	538.5	0.57	5700	0.21	0.7	80	12	2	40	0.01	16	0.01	5.8	43	0.01
KL30-05	538.5	540	0.442	4420	0.15	0.6	60	7	5	234	0.01	12	0.01	3.1	43	0.01
KL30-05	540	542.9	0.7	7000	0.25	0.9	70	12	1	335	0.01	20	0.01	6.3	42	0.01
KL30-05	542.9	546	0.84	8400	0.33	1.3	69	6	5	139	0.01	14	0.3	4.8	32	0.01
KL30-05	546	548.6	1.13	11300	0.37	1.8	90	8	3	212	0.01	18	0.2	6.2	17	0.01
KL30-05	548.6	550.7	0.375	3750	0.25	0.7	50	8	4	19	0.01	9	0.01	3.8	30	0.01
KL30-05	550.7	553	0.69	6900	0.24	0.8	41	6	2	540	0.01	10	0.01	4.0	42	0.01
KL30-05	553	555	0.28	2800	0.1	0.6	33	1	1	50	0.01	6	0.01	3.5	15	0.01
KL30-05	555	558	0.45	4500	0.14	0.9	237	63	14	171	0.01	9	0.5	5.0	22	0.01
KL30-05	558	561	0.47	4700	0.11	3.3	3200	880	160	80	0.01	7	93	6.5	51	0.47
KL30-05	561	564	0.488	4880	0.12	1	43	7	2	44	0.01	10	0.5	5.5	58	0.01
KL30-05	564	567	0.518	5180	0.2	1.3	83	24	2	78	0.01	8	0.6	5.3	54	0.01
KL30-05	567	570	0.78	7800	0.39	1.6	76	6	1	27	0.01	15	0.2	6.0	27	0.01
KL30-05	570	573	0.467	4670	0.28	0.9	75	7	5	15	0.01	14	0.3	4.3	34	0.01
KL30-05	573	576	0.75	7500	0.23	1.5	121	24	120	218	0.01	16	4.6	7.0	31	0.01
KL30-05	576	579	0.37	3700	0.16	0.8	130	30	3	35	0.01	21	0.2	5.0	54	0.01
KL30-05	579	582	0.33	3300	0.14	0.6	118	7	1	28	0.01	16	0.01	3.3	52	0.01
KL30-05	582	585	0.17	1700	0.13	2	314	359	0.01	6	0.01	8	0.7	4.5	48	0.01
KL30-05	585	588	0.28	2800	0.09	0.7	60	5	1	84	0.01	9	0.01	2.8	46	0.01
KL30-05	588	591	0.36	3600	0.26	0.9	65	5	1	15	0.01	8	0.01	4.5	38	0.01
KL30-05	591	594	0.62	6200	0.14	1.1	55	18	2	49	0.01	9	0.3	4.4	98	0.01
KL30-05	594	597	0.21	2100	0.05	0.1	43	10	1	27	0.01	9	0.01	1.3	59	0.01
KL30-05	597	600	0.39	3900	0.09	1.9	153	51	92	189	0.01	11	13.4	5.5	66	0.01
KL30-05	600	603	1.05	10500	0.26	1.7	94	7	2	71	0.01	17	0.3	7.9	20	0.01
KL30-05	603	606	0.26	2600	0.09	0.8	112	6	1	143	0.01	4	0.2	3.3	18	0.01
KL30-05	606	609	0.17	1700	0.07	0.6	50	10	2	51	0.01	4	0.4	2.3	26	0.01
KL30-05	609	612.3	0.224	2240	0.11	28.2	4300	9700	84	57	2	8	9.7	4.4	333	0.72
KL30-05	612.3	614	0.56	5600	0.03	3.6	230	134	74	185	0.01	2	6.8	4.8	108	0.01
KL30-05	614	615.9	0.24	2400	0.03	1.6	214	100	65	134	0.01	4	5.3	3.3	111	0.1
KL30-05	615.9	618	0.44	4400	0.09	1.1	101	36	12	31	0.01	5	0.8	2.5	141	0.01
KL30-05	618	621	0.69	6900	0.24	0.8	48	10	4	86	0.01	12	0.2	5.1	377	0.01
KL30-05	621	624	0.25	2500	0.06	0.5	34	8	15	32	0.01	5	1.2	2.8	120	0.01
KL30-05	624	627	0.56	5600	0.27	4.5	330	134	350	2540	2	9	20	8.5	74	0.2
KL30-05	627	630	0.33	3300	0.1	1.3	48	9	4	280	0.01	7	0.2	4.5	68	0.01
KL30-05	630	632	0.234	2340	0.07	0.7	25	6	2	40	0.01	7	0.01	2.5	51	0.01
KL30-05	632	635	0.26	2600	0.05	1	37	5	0.01	115	0.01	5	0.01	2.5	21	0.01
KL30-05	635	638	0.84	8400	0.23	2.1	78	8	3	25	0.01	23	0.01	9.1	21	0.01
KL30-05	638	641	0.224	2240	0.07	0.6	30	6	2	49	0.01	10	0.01	3.5	14	0.01
KL30-05	641	644	0.405	4050	0.15	1.2	45	6	3	22	0.01	14	0.01	5.3	27	0.01
KL30-05	644	647	1.06	10600	0.39	2.2	111	8	3	23	0.01	38	0.01	8.0	34	0.01
KL30-05	647	648.9	0.7	7000	0.25	1.2	99	9	1	56	0.01	51	0.01	8.5	23	0.01
KL30-05	648.9	651	0.153	1530	0.05	0.1	68	8	2	7	0.01	27	0.01	2.5	30	0.01
KL30-05	651	654	0.79	7900	0.23	1.1	86	9	5	30	0.01	31	0.01	5.4	39	0.01
KL30-05	654	657	0.74	7400	0.18	1	72	9	5	11	0.01	27	0.01	8.3	45	0.01
KL30-05	657	658.5	0.388	3880	0.08	1	103	21	34	340	0.01	25	3.4	4.5	64	0.01
KL30-05	658.5	660	0.056	560	0.05	2.6	2900	470	42	227	0.01	3	7	1.5	391	0.8
KL30-05	660	663	0.0292	292	0.01	0.1	45	22	9	100	0.01	1	1.8	0.5	150	0.01
KL30-05	663	666	0.049	490	0.01	1.4	246	90	19	77	0.01	3	1.8	0.9	140	0.1
KL30-05	666	669	0.0203	203	0.01	0.1	26	7	26	85	0.01	2	2.4	0.6	394	0.01
KL30-05	669	672	0.022	220	0.01	0.1	18	8	37	123	0.01	2	3.2	0.7	410	0.01
KL30-05	672	675	0.0223	223	0.01	0.1	20	17	6	317	0.01	1	1.9	0.9	348	0.01
KL30-05	675	678	0.076	760	0.01	0.1	12	1	2	235	0.01	1	0.8	0.7	286	0.01
KL30-05	678	681	0.043	430	0.01	0.1	12	5	2	54	0.01	4	0.5	0.0	412	0.01
KL30-05	681	684	0.028	280	0.01	0.1	8	1	1	328	0.01	3	0.4	0.0	300	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL30-05	684	687	0.0311		311	0.01	0.1	12	7	0.01	48	0.01	1	0.2	0.6	101	0.01
KL30-05	687	690	0.038		380	0.01	0.1	13	1	0.01	74	0.01	1	0.5	0.0	291	0.01
KL30-05	690	693	0.0295		295	0.01	0.1	13	1	2	129	0.01	1	0.3	0.6	193	0.01
KL30-05	693	696	0.0186		186	0.01	0.1	71	11	0.01	149	0.01	1	0.4	0.0	396	0.01
KL30-05	696	699	0.0089		89	0.01	0.1	19	9	2	114	0.01	2	0.6	0.0	352	0.01
KL30-05	699	702	0.023		230	0.01	0.1	106	150	67	57	0.01	1	5.3	0.0	145	0.1
KL30-05	702	705	0.0094		94	0.01	0.1	24	19	2	197	0.01	2	0.4	0.0	381	0.01
KL30-05	705	707.4	0.0213		213	0.01	0.1	34	31	5	94	0.01	1	0.4	0.0	125	0.01
KL30-05	707.4	709.3	0.011		110	0.01	0.1	32	30	5	193	0.01	1	0.3	0.0	77	0.01
KL30-05	709.3	711.4	0.0227		227	0.01	0.1	78	79	10	172	0.01	1	0.7	0.7	77	0.01
KL30-05	711.4	714.3	0.0175		175	0.01	0.1	92	47	0.01	65	0.01	1	0.5	0.0	165	0.01
KL30-05	714.3	717	0.0201		201	0.01	0.1	74	47	3	67	0.01	1	0.4	0.0	171	0.01
KL30-05	717	720	0.0257		257	0.01	0.1	16	12	13	132	0.01	1	0.4	0.0	119	0.01
KL30-05	720	723	0.0163		163	0.01	0.1	58	17	19	51	0.01	2	0.8	0.0	414	0.01
KL30-05	723	726	0.0151		151	0.01	0.1	25	30	30	62	0.01	1	1	0.0	400	0.01
KL30-05	726	729	0.0293		293	0.01	0.1	94	49	47	76	1	1	5.4	2.2	420	0.01
KL30-05	729	731.5	0.0165		165	0.01	0.1	28	12	9	44	0.01	1	0.2	0.0	144	0.01
KL30-05	731.5	734.5	0.069		690	0.01	1.8	119	900	64	35	0.01	1	8	0.6	86	0.1
KL30-05	734.5	737.5	0.0202		202	0.01	0.7	49	120	66	154	0.01	1	4.6	0.0	368	0.14
KL30-05	737.5	740.5	0.0146		146	0.01	0.1	27	28	42	60	0.01	1	3.2	0.0	341	0.1
KL30-05	740.5	743.5	0.0276		276	0.01	0.1	135	50	10	152	0.01	1	1.8	1.1	224	0.01
KL30-05	743.5	747	0.069		690	0.01	0.1	63	13	4	73	0.01	1	0.3	0.0	204	0.01
KL30-05	747	750	0.099		990	0.01	0.1	40	19	2	95	0.01	1	0.5	0.5	74	0.01
KL30-05	750	753	0.08		800	0.06	0.1	130	60	53	116	9	2	3.1	5.5	35	0.01
KL30-05	753	756	0.082		820	0.01	0.1	10	1	16	113	0.01	1	1.7	1.2	73	0.01
KL30-05	756	759	0.048		480	0.01	0.1	7	8	2	70	0.01	1	0.3	0.0	59	0.01
KL30-05	759	762	0.0165		165	0.01	0.1	21	18	0.01	47	0.01	1	0.3	0.0	123	0.01
KL30-05	762	765	0.0185		185	0.01	0.1	8	12	1	78	0.01	1	0.2	0.0	134	0.01
KL30-05	765	768	0.0237		237	0.01	0.1	13	1	27	179	0.01	1	5.1	0.0	295	0.01
KL30-06	0	3	0.002		20	0.01	0.1	197	16	6	1	0.01	1	0.4	0.0	16	0.01
KL30-06	3	5.5	0.0014		14	0.01	0.1	63	31	13	2	0.01	2	1	0.0	28	0.01
KL30-06	5.5	8	0.0012		12	0.01	0.1	47	27	10	1	0.01	1	0.7	3.0	25	0.01
KL30-06	8	11	0.0015		15	0.01	0.6	500	220	12	4	0.01	1	1.8	2.6	28	0.01
KL30-06	11	14	0.0013		13	0.01	0.7	230	66	11	1	0.01	1	2.9	7.0	32	0.01
KL30-06	14	17	0.0021		21	0.01	0.1	63	38	11	1	0.01	2	1.1	0.0	25	0.01
KL30-06	17	20	0.0035		35	0.01	1.4	291	810	17	1	0.01	2	1.8	2.0	30	0.01
KL30-06	20	23.2	0.0015		15	0.01	0.5	223	180	7	1	0.01	1	1.6	1.2	26	0.01
KL30-06	23.2	26.4	0.0038		38	0.01	0.5	123	128	13	3	0.01	2	2.3	1.2	28	0.01
KL30-06	26.4	31	0.0046		46	0.02	1.3	230	1260	12	2	0.01	1	3.8	4.3	22	0.01
KL30-06	31	34	0.0026		26	0.07	1.2	260	334	25	4	1	1	3.7	1.5	20	0.01
KL30-06	34	37	0.0021		21	0.08	1.7	417	160	31	6	0.01	1	3.3	0.0	24	0.01
KL30-06	37	40	0.0362		362	0.03	0.1	63	50	16	4	0.01	1	1.2	0.0	25	0.01
KL30-06	40	43	0.046		460	0.1	31.2	37300	26300	200	43	35	2	22	29.6	34	0.4
KL30-06	43	46	0.0045		45	0.07	1.4	440	440	23	12	0.01	1	1.5	1.2	21	0.01
KL30-06	46	49	0.0033		33	0.03	0.6	360	350	18	2	0.01	1	1.3	2.5	23	0.01
KL30-06	49	52	0.0085		85	0.03	1	232	206	42	71	1	1	2.7	0.0	38	0.01
KL30-06	52	55	0.0237		237	0.07	2.4	510	510	61	103	3	2	2.1	1.8	32	0.01
KL30-06	55	58	0.0036		36	0.04	0.7	165	180	28	88	2	1	1.4	0.0	19	0.01
KL30-06	58	61	0.079		790	0.14	3.8	2740	2400	48	37	3	2	4.7	2.9	30	0.01
KL30-06	61	64	0.0191		191	0.01	1	780	317	27	81	1	2	1.8	0.0	25	0.01
KL30-06	64	67	0.0157		157	0.02	2.4	580	1230	21	79	3	3	3.1	3.8	62	0.01
KL30-06	67	70	0.0226		226	0.08	5.8	163	4700	37	9	1	2	13.1	3.3	177	0.01
KL30-06	70	73	0.0063		63	0.12	2.1	211	610	22	122	1	3	3.4	1.2	120	0.01
KL30-06	73	76	4.03		40300	2.86	296	7600	37000	7600	163	326	19	122	50.0	124	1.86
KL30-06	76	79	3.31		33100	1.72	32.9	8300	14300	1490	80	23	10	35	12.0	53	1.29
KL30-06	79	82	0.153		1530	0.21	10.5	650	1670	89	147	9	7	8.2	32.0	68	0.01
KL30-06	82	85	0.142		1420	0.1	5	460	880	110	177	4	4	5.9	8.0	209	0.01
KL30-06	85	88	0.0335		335	0.07	1.6	570	256	48	13	1	5	2.8	4.3	218	0.01
KL30-06	88	91	0.0132		132	0.07	3.4	850	430	28	58	4	2	3.5	2.3	48	0.01
KL30-06	91	94	0.074		740	0.17	5.5	1960	430	200	33	2	2	8.8	6.8	190	0.19
KL30-06	94	97	0.0185		185	0.03	2	291	127	41	13	1	3	3.6	3.3	252	0.01
KL30-06	97	100	0.0082		82	0.02	1.9	264	287	18	8	2	2	2.3	1.3	136	0.01
KL30-06	100	103	0.0297		297	0.02	2.7	376	430	30	7	5	1	2.7	0.0	39	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL30-06	103	106	0.0086		86	0.06	3	560	980	41	30	5	2	3.3	0.0	25	0.01
KL30-06	106	109	0.0076		76	0.06	2.5	400	700	64	21	4	1	4.4	2.0	56	0.01
KL30-06	109	112.5	0.0035		35	0.03	1.7	284	600	52	8	2	1	3.6	1.8	24	0.01
KL30-06	112.5	115	0.0126		126	0.17	8.6	4070	3100	32	25	19	3	8.9	5.4	52	0.01
KL30-06	115	118	0.0153		153	0.12	15.9	7200	9300	29	5	16	1	11	3.5	41	0.1
KL30-06	118	120.5	0.0109		109	0.12	35	3540	5800	46	7	61	4	7.9	3.8	14	0.01
KL30-06	120.5	123.5	0.005		50	0.04	5.6	1120	1260	10	4	1	1	6.2	0.0	20	0.01
KL30-06	123.5	126.3	0.0172		172	0.06	15.6	10400	6700	40	4	5	1	24	2.7	18	0.14
KL30-06	126.3	129.6	0.003		30	0.03	5.1	1190	2200	8	2	2	1	6.4	1.7	21	0.01
KL30-06	129.6	132.1	0.0035		35	0.06	5.1	1000	1930	16	4	6	1	3.3	3.8	24	0.01
KL30-06	132.1	134.5	0.0215		215	0.03	3.2	374	1280	12	7	3	1	2.8	3.8	23	0.01
KL30-06	134.5	138.3	0.14		1400	0.15	10.7	2110	4500	130	40	5	1	10	5.9	33	0.11
KL30-06	138.3	141.3	0.0355		355	0.17	14.5	3700	6900	90	71	4	1	16.7	4.8	38	0.01
KL30-06	141.3	144.3	0.0109		109	0.05	2	283	540	20	15	1	1	2.3	1.2	35	0.01
KL30-06	144.3	147	0.0076		76	0.03	1.7	197	880	12	6	0.01	1	1.9	0.0	28	0.01
KL30-06	147	150	0.0033		330	0.06	7.3	2300	4900	21	21	6	1	4.7	2.8	33	0.1
KL30-06	150	152.5	0.0079		79	0.04	4.8	310	2500	5	46	4	1	4.2	3.2	35	0.01
KL30-06	152.5	155.5	0.0026		26	0.03	3	413	2100	8	16	4	1	3.2	2.8	31	0.01
KL30-06	155.5	158.4	0.0015		15	0.07	2.1	330	830	14	10	1	1	2.3	2.0	24	0.01
KL30-06	158.4	161.4	0.0017		17	0.01	2.4	2050	1430	7	19	1	1	2.3	2.8	18	0.01
KL30-06	161.4	164.7	0.0022		22	0.03	3.3	1310	2050	5	18	0.01	1	2.9	2.0	14	0.01
KL30-06	164.7	167.5	0.0027		27	0.01	3.1	1920	1810	8	15	2	1	3.5	4.0	15	0.01
KL30-06	167.5	170.6	0.0125		125	0.05	7.3	2600	3000	13	12	1	1	4	2.5	12	0.01
KL30-06	170.6	173	0.0102		102	0.07	6	5100	3800	30	13	1	1	4.9	4.5	17	0.12
KL30-06	173	176.9	0.058		580	0.29	83	80000	93700	89	109	2	1	83	13.5	22	0.2
KL30-06	176.9	179.9	0.0057		57	0.04	7.2	12000	12900	6	118	0.01	1	5	3.8	28	0.01
KL30-06	179.9	182.5	0.0045		45	0.01	1.9	1870	2500	5	55	0.01	1	2	0.0	19	0.01
KL30-06	182.5	186	0.0053		53	0.02	2.5	4100	2700	8	61	0.01	1	3	2.0	14	0.01
KL30-06	186	189	0.0038		38	0.01	1.2	730	1060	8	58	0.01	1	1.3	2.3	17	0.01
KL30-06	189	193	0.0263		263	0.61	62	77000	56600	15	207	14	1	60	77.0	23	0.01
KL30-06	193	195.3	0.0027		27	0.05	3.6	1460	3900	13	34	0.01	1	3.2	5.2	23	0.01
KL30-06	195.3	198.1	0.0048		48	0.05	1.5	720	1970	15	75	0.01	1	1.5	1.5	17	0.01
KL30-06	198.1	200.5	0.0073		73	0.07	4.2	2530	4700	13	55	0.01	1	3.8	5.8	17	0.01
KL30-06	200.5	202.6	0.0025		25	0.02	1	167	361	5	64	0.01	1	0.9	0.0	20	0.01
KL30-06	202.6	206	0.0034		34	0.01	1.5	550	1010	7	26	0.01	1	2	1.9	19	0.01
KL30-06	206	208.5	0.0038		38	0.02	13.1	12600	10100	9	9	0.01	1	16.8	12.8	18	0.01
KL30-06	208.5	212.5	0.0033		33	0.01	2.3	2360	1540	8	23	1	1	2	3.0	71	0.01
KL30-06	212.5	215.5	0.0027		27	0.02	1.7	900	1120	13	10	1	1	2.1	3.8	18	0.01
KL30-06	215.5	218.5	0.0024		24	0.02	1.3	640	760	9	10	1	1	1.6	1.8	16	0.01
KL30-06	218.5	221	0.002		20	0.01	0.8	450	520	7	11	0.01	1	1.3	1.3	14	0.01
KL30-06	221	223	0.052		520	0.15	30.3	59500	42700	60	131	10	2	22	160.0	25	0.21
KL30-06	223	227.1	0.0065		65	0.07	9.4	5500	7300	17	40	12	1	6.5	32.8	26	0.01
KL30-06	227.1	230.1	0.0066		66	0.02	2.1	650	520	18	21	5	2	1.9	2.3	17	0.01
KL30-06	230.1	233.2	0.0047		47	0.03	5.7	1680	2060	7	62	17	2	1.1	4.0	21	0.01
KL30-06	233.2	236	0.0102		102	0.1	29.3	3560	5700	21	173	76	6	2	7.5	24	0.11
KL30-06	236	238.7	0.005		50	0.01	3.8	350	800	8	50	11	2	1.1	2.8	22	0.01
KL30-06	238.7	242.5	0.006		60	0.02	15.2	1180	1750	13	29	36	1	3	5.8	24	0.01
KL30-06	242.5	248	0.0043		43	0.01	1.3	850	530	8	12	3	1	1.4	3.2	24	0.01
KL30-06	248	253	0.047		470	0.07	2.1	2640	1100	34	47	6	3	2.6	4.8	21	0.18
KL30-06	253	256	0.0124		124	0.96	7.2	3530	1600	15	1040	26	3	4.4	4.4	103	0.22
KL30-06	256	259	0.0163		163	2.69	26	9000	6100	120	580	22	2	7.8	13.3	82	0.4
KL30-06	259	262	0.0088		88	1.19	3	780	362	25	2100	4	5	2.7	8.3	52	0.01
KL30-06	262	265	0.0101		101	0.45	2.5	830	400	29	263	6	2	2	8.0	178	0.21
KL30-06	265	268	0.046		460	0.28	3.4	6800	790	160	23	24	5	6.6	6.1	22	0.6
KL30-06	268	271	0.22		2200	1.52	6.9	15300	8000	210	198	22	15	22	15.2	45	2.69
KL30-06	271	274	0.2		2000	0.33	4.8	4600	1020	560	1100	10	13	20.3	7.0	25	0.85
KL30-06	274	277	0.043		430	0.07	0.1	1470	132	27	163	1	3	1.3	4.5	23	0.01
KL30-06	277	280	0.158		1580	0.25	1	4200	205	30	1050	3	3	1	6.8	21	0.01
KL30-06	280	284.5	0.074		740	0.11	1.2	9200	130	19	43	9	10	1.4	9.5	31	0.01
KL30-06	284.5	287.5	0.13		1300	0.12	2.4	2100	820	52	25	5	4	3.7	10.0	25	0.11
KL30-06	287.5	290.5	0.2		2000	0.24	6.1	13900	810	44	22	15	14	3.4	12.8	24	0.1
KL30-06	290.5	293.5	0.21		2100	0.43	1.6	1470	98	32	31	5	13	1.3	9.0	24	0.01
KL30-06	293.5	296.5	0.72		7200	0.79	3.5	470	66	17	114	3	58	2.3	19.3	43	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL30-06	296.5	299.5	0.148	1480	0.37	2.2	1250	257	36	700	3	8	3.6	14.0	50	0.1
KL30-06	299.5	302.5	0.46	4600	0.89	4.3	2630	830	420	219	2	48	22	30.4	72	0.19
KL30-06	302.5	305.5	0.2	2000	0.85	35	21900	21700	290	8	2	5	36	22.8	62	0.48
KL30-06	305.5	308	0.57	5700	1.62	41	35400	21200	140	45	5	52	24	26.8	56	0.46
KL30-06	308	310	1.51	15100	1.31	8.7	2100	100	32	34	6	92	2	29.2	99	0.01
KL30-06	310	313	1.04	10400	0.66	4.8	870	260	10	17	11	110	1.6	66.0	35	0.01
KL30-06	313	316														
KL30-06	316	319	1.85	18500	1.22	7.1	920	185	19	47	5	37	2.7	16.8	29	0.01
KL30-06	319	321.5	3.06	30600	1.84	10.7	287	43	6	9	4	58	0.6	34.5	31	0.01
KL30-06	321.5	323.5	2.29	22900	1.38	9.7	720	1110	8	28	1	22	3.2	19.2	33	0.01
KL30-06	323.5	326.5	2.06	20600	1.18	28	9300	10800	52	5	3	24	13	23.0	86	0.18
KL30-06	326.5	329	2.2	22000	1.57	27	3900	3200	28	6	7	21	6.2	16.0	38	0.15
KL30-06	329	331	1.89	18900	0.78	3.5	600	103	6	30	10	38	0.8	18.5	24	0.01
KL30-06	331	334	3.12	31200	1.26	8.6	480	149	19	13	4	34	2.9	18.0	30	0.01
KL30-06	334	336	3.14	31400	2.03	4.9	780	77	8	35	4	52	0.7	23.0	37	0.01
KL30-06	336	338	4.3	43000	2.56	17.2	790	225	27	15	5	107	0.8	26.0	222	0.18
KL30-06	338	340.4	2.83	28300	0.18	7.5	47	76	7500	329	1	18	378	13.0	79	0.19
KL30-06	340.4	344.5	1.25	12500	0.6	3.1	357	199	89	155	2	21	5.1	16.0	223	0.12
KL30-06	344.5	347.5	1.64	16400	0.43	2	97	49	100	156	1	17	1.5	14.8	325	0.22
KL30-06	347.5	350.5	1.4	14000	0.43	1.6	96	24	5	89	1	20	0.01	12.5	12	0.01
KL30-06	350.5	353.5	1.83	18300	0.39	1.8	68	23	12	720	1	14	1.3	8.0	237	0.01
KL30-06	353.5	356.5	1.53	15300	0.31	2.5	219	96	3	630	0.01	16	1	8.5	82	0.01
KL30-06	356.5	359.5	1.5	15000	0.36	2.2	367	340	9	690	0.01	20	1	10.5	107	0.01
KL30-06	359.5	361.5	2.07	20700	0.42	1.9	56	31	1	1050	1	26	0.2	9.5	123	0.01
KL30-06	361.5	364	2.33	23300	0.59	2.8	131	32	9	960	0.01	24	1	10.5	250	0.01
KL30-06	364	367	1.09	10900	0.41	1.2	80	31	2	201	0.01	16	0.2	8.8	90	0.01
KL30-06	367	370	1.03	10300	0.33	1.5	230	34	2	203	1	18	0.2	7.3	169	0.01
KL30-06	370	373	1.69	16900	0.62	3	84	75	59	490	0.01	12	5	5.0	254	0.01
KL30-06	373	376	1.33	13300	0.52	2.2	171	66	3	94	0.01	11	0.3	1.5	137	0.01
KL30-06	376	379	1.16	11600	0.42	2	253	35	8	109	2	14	0.4	4.3	88	0.01
KL30-06	379	382	1.71	17100	0.99	2.3	76	30	2	32	1	13	0.5	4.5	114	0.1
KL30-06	382	385	1.24	12400	0.81	3.8	202	470	6	34	2	14	1.1	4.8	118	0.01
KL30-06	385	388	1.16	11600	0.9	1.7	48	33	3	30	3	10	0.4	5.0	97	0.01
KL30-06	388	390	0.98	9800	0.65	2.2	61	41	32	85	2	14	2	4.0	81	0.1
KL30-06	390	393	1.31	13100	0.67	2.3	60	26	4	180	2	16	0.3	6.0	71	0.01
KL30-06	393	396	1.33	13300	0.6	2.1	72	45	22	139	1	11	0.7	5.0	91	0.01
KL30-06	396	399	1.31	13100	0.62	3.2	240	100	16	76	1	11	0.3	10.0	69	0.1
KL30-06	399	402	1.35	13500	0.6	5.5	101	81	14	151	8	14	1.6	10.2	63	0.1
KL30-06	402	405	0.98	9800	0.57	2.3	64	14	2	201	1	18	0.01	7.0	87	0.01
KL30-06	405	408	1.51	15100	1.73	2.8	66	15	3	103	1	14	0.3	17.0	65	0.01
KL30-06	408	411	2.17	21700	2.22	2.3	58	10	2	69	1	15	0.3	17.8	98	0.01
KL30-06	411	414	1.65	16500	1.25	2.5	28	12	13	422	4	6	0.2	10.5	74	0.01
KL30-06	414	417	1.45	14500	0.6	3.2	83	30	10	953	4	5	1.3	5.5	69	0.1
KL30-06	417	420	1.02	10200	0.25	1.9	58	48	11	336	2	5	4.1	6.0	80	0.01
KL30-06	420	423	0.95	9500	0.35	1.8	28	23	0.01	103	3	4	1	5.5	97	0.01
KL30-06	423	426	4.9	49000	0.68	23.5	1280	2310	150	32	5	7	180	2.5	62	0.12
KL30-06	426	429	0.59	5900	0.2	4.3	307	730	43	153	5	10	90	7.5	125	0.01
KL30-06	429	432	0.55	5500	0.14	2.4	173	195	29	54	2	4	6.3	5.3	179	0.01
KL30-06	432	434.5	0.88	8800	0.25	3.3	1010	327	61	24	4	5	22	7.1	151	0.1
KL30-06	434.5	437	1.23	12300	0.29	2.9	78	70	220	6	1	5	4.8	6.0	157	0.01
KL30-06	437	440	0.68	6800	0.13	1.9	500	161	27	9	2	3	2.3	5.3	135	0.01
KL30-06	440	443.3	0.445	4450	0.12	1.3	420	222	15	9	0.01	3	1.2	4.1	96	0.01
KL30-06	443.3	446.4	0.536	5360	0.3	0.9	27	14	1	14	0.01	5	0.3	5.5	96	0.01
KL30-06	446.4	449.5	0.54	5400	0.67	0.7	35	16	1	8	1	3	0.2	5.5	105	0.01
KL30-06	449.5	453	0.65	6500	0.35	2.3	700	328	2	80	2	4	0.8	6.0	65	0.01
KL30-06	453	456	0.57	5700	0.43	2	386	217	5	42	2	8	0.4	5.5	61	0.01
KL30-06	456	459	0.87	8700	0.53	2.5	500	267	19	14	2	6	1.5	6.6	264	0.01
KL30-06	459	462	0.56	5600	0.22	1.8	240	146	10	52	3	4	1.7	5.5	186	0.12
KL30-06	462	465	0.468	4680	0.26	1.3	121	60	27	11	3	3	0.4	5.3	182	0.1
KL30-06	465	468	0.6	6000	0.33	1.4	48	38	42	16	2	4	0.5	5.5	101	0.01
KL30-06	468	471	0.98	9800	0.56	4.4	300	207	170	133	3	7	7.3	7.4	215	0.01
KL30-06	471	474	0.87	8700	0.53	1.7	218	124	13	82	2	6	1.5	8.3	211	0.01
KL30-06	474	477	1.18	11800	1.12	1.9	183	75	1	79	2	10	1.3	5.7	135	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL30-06	477	480	1.15	11500	1.28	3	64	44	28	34	5	3	1.3	8.0	165	0.01
KL30-06	480	483	1.09	10900	0.55	3.2	570	272	20	17	5	5	6.9	12.0	290	0.1
KL30-06	483	486	0.93	9300	0.28	3	800	327	50	44	2	7	11.2	11.1	137	0.01
KL30-06	486	489	1.33	13300	0.34	6.3	382	137	210	20	8	5	26	12.5	242	0.01
KL30-06	489	492	0.96	9600	0.45	4.1	400	220	180	40	6	14	15	13.0	264	0.01
KL30-06	492	495	0.89	8900	0.52	3	128	83	18	14	2	8	2.1	12.0	276	0.01
KL30-06	495	498	0.75	7500	0.73	1.9	164	106	33	17	2	6	6.9	11.0	120	0.01
KL30-06	498	500.6	0.84	8400	0.52	2.6	1550	1140	57	16	3	3	17.4	10.3	148	0.33
KL30-06	500.6	504	0.429	4290	0.26	1.8	480	332	30	29	1	4	1.2	6.8	156	0.01
KL30-06	504	507	0.74	7400	0.33	2.2	204	138	54	46	2	5	4.5	7.8	229	0.01
KL30-06	507	510	0.83	8300	0.44	1.5	42	19	12	39	0.01	6	0.4	7.5	134	0.01
KL30-06	510	513	0.55	5500	0.29	0.9	37	17	2	66	0.01	5	0.01	5.6	142	0.01
KL30-06	513	516	0.78	7800	0.43	1.3	39	18	4	36	0.01	8	0.2	7.5	132	0.01
KL30-06	516	519	0.64	6400	0.31	1.4	47	8	7	46	0.01	9	0.2	8.8	140	0.01
KL30-06	519	522	2.02	20200	0.97	2.7	72	17	5	193	0.01	22	0.2	11.0	215	0.01
KL30-06	522	525	0.72	7200	0.39	1.3	31	8	3	68	0.01	10	0.3	9.5	170	0.01
KL30-06	525	528	0.51	5100	0.27	1.4	27	12	3	58	0.01	10	0.8	7.8	273	0.01
KL30-06	528	531	0.62	6200	0.25	1.3	440	298	500	40	0.01	11	6.5	6.4	221	0.01
KL30-06	531	534	0.69	6900	0.31	4.3	304	240	110	73	14	8	7.3	10.0	60	0.01
KL30-06	534	537	0.53	5300	0.29	0.8	28	11	5	62	0.01	5	0.01	5.5	174	0.01
KL30-06	537	540	0.59	5900	0.36	0.9	75	36	13	49	0.01	7	0.3	5.5	198	0.01
KL30-06	540	543	0.45	4500	0.16	0.7	95	60	24	41	0.01	4	0.4	5.0	201	0.01
KL30-06	543	546	0.295	2950	0.11	1.7	380	420	88	97	1	2	15.9	5.6	207	0.01
KL30-06	546	549	0.489	4890	0.12	1.7	610	370	42	363	1	5	12.7	6.8	83	0.01
KL30-06	549	552	0.65	6500	0.35	0.9	130	56	3	46	0.01	7	0.2	6.3	147	0.01
KL30-06	552	555	0.75	7500	0.21	1	81	45	10	80	0.01	5	2	7.8	102	0.01
KL30-06	555	558	0.79	7900	0.51	1.2	138	45	36	99	0.01	6	0.9	7.5	91	0.01
KL30-06	558	561	0.77	7700	0.24	1.3	237	72	73	88	0.01	4	2.8	10.0	135	0.01
KL30-06	561	564	0.75	7500	0.22	2.8	860	440	260	60	2	6	18.3	6.6	136	0.17
KL30-06	564	567	0.56	5600	0.1	1	94	27	77	31	0.01	5	0.8	7.0	123	0.01
KL30-06	567	570	0.57	5700	0.13	0.8	26	8	7	52	0.01	5	0.2	7.3	212	0.01
KL30-06	570	573	0.412	4120	0.09	1.1	107	62	18	47	1	2	4.6	4.8	150	0.1
KL30-06	573	576	0.83	8300	0.29	4.6	123	100	260	289	7	6	124	12.3	75	0.13
KL30-06	576	579	0.82	8200	0.15	1.6	103	51	70	79	0.01	6	2.2	6.5	144	0.01
KL30-06	579	582	0.83	8300	0.06	1.1	167	45	160	100	0.01	5	1.2	7.9	160	0.01
KL30-06	582	585	0.77	7700	0.11	0.9	214	64	160	78	0.01	3	1.1	6.3	86	0.01
KL30-06	585	588	0.405	4050	0.07	1	164	57	30	90	0.01	2	3.7	4.7	89	0.01
KL30-06	588	591	0.78	7800	0.07	6.1	314	130	560	77	1	2	85	7.3	201	0.12
KL30-06	591	594	3.43	34300	0.36	35.6	660	166	2400	110	3	6	278	16.5	84	0.15
KL30-06	594	597	0.95	9500	0.08	8.2	38	55	25	84	1	3	2.4	5.5	125	0.01
KL30-06	597	600	0.513	5130	0.08	1.7	141	85	9	77	1	8	1.8	7.5	160	0.01
KL30-06	600	603	0.82	8200	0.05	1.4	187	101	50	421	0.01	4	2.5	5.8	67	0.01
KL30-06	603	606	0.85	8500	0.15	5.5	870	380	1380	98	2	7	62	4.8	73	0.15
KL30-06	606	609	0.435	4350	0.2	1	82	50	10	95	0.01	7	0.5	4.0	174	0.01
KL30-06	609	612	0.401	4010	0.14	0.8	58	61	4	101	0.01	7	0.3	3.9	135	0.01
KL30-06	612	615	0.29	2900	0.07	4.6	150	100	4	81	12	3	0.4	2.8	221	0.01
KL30-06	615	618	0.33	3300	0.05	0.7	56	62	16	135	0.01	3	0.2	4.0	128	0.01
KL30-06	618	621	0.483	4830	0.24	1.3	373	116	25	194	1	6	2	4.7	199	0.1
KL30-06	621	624	0.29	2900	0.06	2.5	317	262	41	55	4	4	5.3	7.3	110	0.01
KL30-06	624	627	0.364	3640	0.03	2	292	229	100	103	2	5	4.6	4.0	181	0.01
KL30-06	627	630	0.31	3100	0.02	1.6	123	138	100	101	1	4	7.5	3.4	178	0.01
KL30-06	630	633	0.357	3570	0.04	1.5	670	278	71	297	2	6	2.9	3.8	110	0.17
KL30-06	633	636	0.31	3100	0.03	1.6	530	251	100	148	2	6	7.5	6.5	175	0.1
KL30-06	636	638.2	0.364	3640	0.05	2.1	1070	379	180	258	2	5	8.1	5.8	100	0.01
KL30-06	638.2	640.2	0.3	3000	0.03	1.9	680	291	59	326	2	4	10.8	5.5	196	0.01
KL30-06	640.2	642	0.62	6200	0.23	1.2	127	16	0.01	126	0.01	26	0.2	7.0	70	0.01
KL30-06	642	645	0.3	3000	0.15	0.9	120	12	0.01	35	0.01	25	0.2	3.4	51	0.01
KL30-06	645	648	0.33	3300	0.32	1.1	112	8	0.01	9	0.01	37	0.01	7.3	30	0.01
KL30-06	648	651	0.26	2600	0.24	1	130	8	0.01	5	0.01	43	0.7	4.5	35	0.01
KL30-06	651	654	1.08	10800	0.8	2.1	60	12	0.01	16	0.01	96	0.01	18.0	28	0.01
KL30-06	654	657	0.93	9300	0.35	1.9	106	13	1	17	0.01	54	0.2	12.8	32	0.01
KL30-06	657	659.5	1.38	13800	0.52	3.3	221	12	4	54	0.01	42	0.2	9.5	33	0.01
KL30-06	659.5	662	0.99	9900	0.33	2.4	161	8	5	23	0.01	41	0.01	10.8	40	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL30-06	662	665	0.67	6700	0.22	1.7	159	11	3	3	0.01	30	0.01	5.8	50	0.01
KL30-06	665	668.5	0.34	3400	0.13	1	70	14	8	2	0.01	26	0.3	5.8	45	0.01
KL30-06	668.5	671.5	0.107	1070	0.05	0.1	54	7	5	19	0.01	14	0.01	2.3	26	0.01
KL30-06	671.5	674.6	0.481	4810	0.36	1.2	111	14	22	9	0.01	27	0.5	6.0	34	0.01
KL30-06	674.6	677.4	0.24	2400	0.14	0.5	89	15	3	7	0.01	25	0.2	2.3	32	0.01
KL30-06	677.4	680.4	0.0109	109	0.01	0.1	62	19	1	2	0.01	16	0.01	0.0	37	0.01
KL30-06	680.4	684	0.107	1070	0.12	0.1	78	9	2	5	0.01	25	0.01	1.8	47	0.01
KL30-06	684	687	0.452	4520	0.2	1.1	175	12	5	8	1	19	0.3	5.0	50	0.01
KL30-06	687	690	0.25	2500	0.13	0.5	88	10	2	4	0.01	22	0.01	3.8	66	0.01
KL30-06	690	693	0.454	4540	0.17	1	105	10	2	8	0.01	44	0.2	4.9	45	0.01
KL30-06	693	696	0.235	2350	0.09	0.6	74	7	1	32	0.01	31	0.01	3.0	53	0.01
KL30-06	696	699.5	0.35	3500	0.14	1	76	18	2	48	0.01	18	0.3	4.0	125	0.01
KL30-06	699.5	702	0.161	1610	0.05	0.1	41	11	3	230	0.01	9	0.2	1.5	100	0.01
KL30-06	702	705	0.072	720	0.02	0.1	36	15	6	37	0.01	4	0.01	1.0	51	0.01
KL30-06	705	708.1	1.17	11700	0.26	8.9	620	272	8	59	2	18	3.2	6.0	45	0.01
KL30-06	708.1	709.8	0.83	8300	0.39	35.2	4860	4400	120	56	42	4	28	13.0	120	0.2
KL30-06	709.8	713	1.93	19300	0.8	24.4	1200	890	190	53	22	16	24	18.4	134	0.01
KL30-06	713	716	0.45	4500	0.04	6.1	126	102	27	36	3	6	12.8	6.5	160	0.01
KL30-06	716	718	0.16	1600	0.01	1.8	73	38	17	32	0.01	3	8.3	3.0	183	0.01
KL30-06	718	721.1	0.149	1490	0.05	1	45	26	5	8	0.01	3	1.2	1.5	105	0.01
KL30-06	721.1	725.7	0.257	2570	0.03	1.2	171	77	54	194	0.01	4	7.8	5.3	174	0.01
KL30-06	725.7	728.7	0.091	910	0.02	0.1	17	8	4	70	0.01	3	0.3	2.0	25	0.01
KL30-06	728.7	731.7	0.072	720	0.05	0.6	101	87	23	31	1	12	4.4	5.0	32	0.01
KL30-06	731.7	734.7	0.165	1650	0.04	1	50	27	15	43	0.01	5	1.1	4.8	19	0.01
KL30-06	734.7	736.6	0.078	780	0.03	0.1	25	12	9	5	0.01	8	0.01	3.5	15	0.01
KL30-06	736.6	740.7	0.113	1130	0.04	0.1	68	9	2	8	0.01	21	0.01	2.0	37	0.01
KL30-06	740.7	743.7	0.356	3560	0.12	0.9	82	9	0.01	37	0.01	30	0.01	5.0	39	0.01
KL30-06	743.7	746.7	0.27	2700	0.06	0.6	88	7	0.01	96	0.01	20	0.01	3.0	38	0.01
KL30-06	746.7	749.7	0.13	1300	0.05	0.5	65	8	0.01	6	0.01	18	0.01	1.8	34	0.01
KL30-06	749.7	752.7	0.091	910	0.01	0.1	67	13	3	27	0.01	26	0.2	6.3	51	0.01
KL30-06	752.7	755.4	0.158	1580	0.04	0.1	112	7	1	6	0.01	17	0.01	2.8	58	0.01
KL30-06	755.4	758.7	1.2	12000	0.42	3	114	10	3	21	0.01	30	0.01	8.8	43	0.01
KL30-06	758.7	761.7	1.2	12000	0.3	2.5	157	42	2	23	0.01	27	0.2	10.2	23	0.01
KL30-06	761.7	764.7	0.77	7700	0.2	2.1	96	14	2	11	0.01	27	0.01	10.3	26	0.01
KL30-06	764.7	767.7	0.217	2170	0.17	0.7	92	9	1	3	0.01	19	0.01	2.5	33	0.01
KL30-06	767.7	770.7	0.53	5300	0.27	1.3	91	9	2	2	0.01	22	0.01	5.0	38	0.01
KL30-06	770.7	772.7	1.19	11900	0.48	2.3	118	10	2	20	0.01	23	0.01	6.9	48	0.01
KL30-06	772.7	775.7	0.82	8200	0.24	1.6	72	11	2	23	0.01	33	0.2	15.3	26	0.01
KL30-06	775.7	778.7	0.446	4460	0.25	0.8	84	19	1	13	0.01	27	0.01	5.8	28	0.01
KL30-06	778.7	781.7	0.515	5150	0.26	0.7	100	90	1	13	0.01	8	2.1	4.8	55	0.01
KL30-06	781.7	784.2	0.491	4910	0.15	2.8	650	283	11	50	4	5	12	6.0	128	0.11
KL30-06	784.2	787.1	0.096	960	0.01	1.3	1840	920	24	23	1	3	7	2.5	168	0.19
KL30-06	787.1	791.7	0.115	1150	0.02	1.1	690	580	5	41	0.01	5	1.6	2.3	113	0.01
KL30-06	791.7	794.7	0.086	860	0.01	0.1	41	15	4	50	0.01	4	0.01	0.8	159	0.01
KL30-06	794.7	798	0.172	1720	0.01	0.1	43	16	9	16	0.01	4	0.9	0.8	108	0.01
KL30-07	0	4	0.0015	15	0.01	0.1	63	32	6	2	0.01	1	0.5	0.8	49	0.01
KL30-07	4	7	0.0021	21	0.01	0.1	42	24	7	4	0.01	1	0.6	1.0	19	0.01
KL30-07	7	10	0.0014	14	0.01	0.1	156	70	10	3	0.01	3	0.8	1.0	26	0.01
KL30-07	10	13	0.0013	13	0.01	0.1	189	57	12	3	0.01	3	1.1	1.5	40	0.01
KL30-07	13	16	0.0014	14	0.01	0.1	63	50	14	4	0.01	1	0.7	0.9	23	0.01
KL30-07	16	19	0.0036	36	0.01	0.1	98	56	10	3	0.01	1	0.9	2.6	22	0.01
KL30-07	19	22	0.0018	18	0.01	0.1	26	25	9	2	0.01	2	0.4	0.0	27	0.01
KL30-07	22	26.5	0.0015	15	0.01	0.1	59	28	11	3	0.01	1	0.5	0.6	24	0.01
KL30-07	26.5	29.5	0.0043	43	0.04	0.7	135	135	16	2	0.01	1	0.8	0.9	21	0.01
KL30-07	29.5	32.5	0.0029	29	0.01	0.6	560	238	3	1	0.01	1	0.8	2.4	18	0.01
KL30-07	32.5	35.5	0.0032	32	0.01	0.7	410	297	6	1	0.01	1	0.7	1.3	17	0.01
KL30-07	35.5	38	0.0023	23	0.01	0.1	72	91	6	2	0.01	1	0.7	1.3	22	0.01
KL30-07	38	41	0.0025	25	0.01	0.1	120	180	11	1	0.01	3	0.5	1.3	17	0.01
KL30-07	41	44.5	0.0265	265	0.01	0.7	166	240	61	3	1	2	2.9	2.3	22	0.01
KL30-07	44.5	47.5	0.0032	32	0.01	0.1	69	117	5	1	0.01	1	0.5	0.8	22	0.01
KL30-07	47.5	50.5	0.0031	31	0.01	1.6	221	325	22	1	0.01	1	4.1	1.0	23	0.01
KL30-07	50.5	53.5	0.0026	26	0.03	0.1	181	161	23	1	0.01	1	0.9	1.6	28	0.01
KL30-07	53.5	56.5	0.0019	19	0.04	0.1	137	166	26	2	0.01	1	1.1	1.7	24	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL30-07	56.5	59.5	0.0015		15	0.02	0.1	86	118	17	1	0.01	3	0.6	3.1	16	0.01
KL30-07	59.5	62.5	0.0019		19	0.01	0.1	74	175	18	1	0.01	1	0.6	1.1	17	0.01
KL30-07	62.5	65.5	0.0057		57	0.01	0.1	93	91	8	1	0.01	1	0.6	1.7	31	0.01
KL30-07	65.5	68.5	0.0047		47	0.01	0.1	63	86	10	3	0.01	1	0.6	1.3	33	0.01
KL30-07	68.5	71.5	0.0032		32	0.01	0.1	66	62	8	2	0.01	1	0.5	1.2	23	0.01
KL30-07	71.5	74.5	0.0019		19	0.01	0.1	30	32	4	1	0.01	1	0.4	1.2	12	0.01
KL30-07	74.5	77.5	0.0024		24	0.01	0.1	92	192	18	1	0.01	1	0.7	0.7	23	0.01
KL30-07	77.5	80.5	0.0018		18	0.01	0.1	29	35	1	1	0.01	1	0.5	0.6	17	0.01
KL30-07	80.5	83.5	0.0076		76	0.01	0.1	111	100	9	3	0.01	1	0.6	1.1	28	0.01
KL30-07	83.5	86.5	0.0035		35	0.01	0.1	186	87	15	3	0.01	1	0.6	1.5	27	0.01
KL30-07	86.5	89.5	0.0034		34	0.01	0.1	90	90	3	2	0.01	2	0.4	0.9	21	0.01
KL30-07	89.5	92.5	0.004		40	0.01	0.1	60	65	3	1	0.01	1	0.5	1.3	25	0.01
KL30-07	92.5	95.5	0.0067		67	0.02	0.1	92	134	9	1	1	1	0.8	2.6	22	0.01
KL30-07	95.5	98.5	0.0073		73	0.01	0.7	99	261	6	2	1	1	0.6	2.9	18	0.01
KL30-07	98.5	103	0.0027		27	0.01	0.1	100	73	5	1	0.01	1	0.2	1.2	25	0.01
KL30-07	103	107.5	0.0052		52	0.01	0.1	92	61	7	1	0.01	1	0.5	1.0	38	0.01
KL30-07	107.5	110.5	0.0031		31	0.01	0.1	186	137	16	1	0.01	3	0.9	0.8	58	0.01
KL30-07	110.5	113.5	0.0068		68	0.01	0.6	222	145	42	3	0.01	2	1.3	1.2	82	0.01
KL30-07	113.5	116.5	0.124		1240	0.02	2	450	321	180	8	5	5	5.9	2.1	100	0.01
KL30-07	116.5	119.5	0.0089		89	0.29	5.8	1400	1910	110	5	3	3	5.6	15.0	56	0.1
KL30-07	119.5	120.9	0.078		780	0.94	66	9900	27300	1030	45	52	4	42	75.0	34	0.35
KL30-07	120.9	124	0.0166		166	0.83	16.3	6900	6200	300	20	9	3	18.6	22.0	17	0.25
KL30-07	124	127.3	0.0221		221	0.63	32.7	11800	15800	170	10	25	3	34	47.0	22	0.21
KL30-07	127.3	131.5	0.0116		116	0.98	11	3000	4800	100	7	2	2	15.3	7.0	145	0.18
KL30-07	131.5	134.5	0.22		2200	1.17	118	58400	68000	630	45	5	1	162	24.0	116	1.27
KL30-07	134.5	137.5	0.0185		185	0.45	14.8	2000	8900	140	11	3	1	19.3	4.4	100	0.11
KL30-07	137.5	140.5	0.0068		68	0.15	2.9	1120	1110	23	8	1	1	3.3	1.5	173	0.01
KL30-07	140.5	143.5	0.0049		49	0.56	3.5	920	1180	39	10	1	1	5	2.2	124	0.1
KL30-07	143.5	146	0.0118		118	0.05	1	139	327	12	5	0.01	1	1.3	1.4	108	0.01
KL30-07	146	149.6	0.0047		47	0.1	1.1	90	220	27	10	1	2	1.4	1.1	132	0.01
KL30-07	149.6	152.5	0.0054		54	0.06	0.8	137	114	28	8	2	1	1.1	1.2	147	0.01
KL30-07	152.5	155.3	0.0078		78	0.05	0.7	106	125	17	8	1	1	0.8	0.8	133	0.01
KL30-07	155.3	158.8	0.0073		73	0.05	1.6	116	413	33	5	5	1	1.7	0.9	156	0.01
KL30-07	158.8	161.5	0.0044		44	0.21	1.5	206	304	41	7	3	1	1.8	1.4	131	0.01
KL30-07	161.5	164.5	0.0109		109	0.21	2.8	267	610	31	12	7	2	2.6	2.3	23	0.01
KL30-07	164.5	169	0.59		5900	0.16	2.2	400	610	140	42	5	3	8.4	5.1	69	0.01
KL30-07	169	172	0.0241		241	0.16	1.2	267	410	40	22	2	1	4.2	2.2	42	0.01
KL30-07	172	175	0.0378		378	0.26	3.5	350	500	150	76	12	2	4.8	3.5	22	0.01
KL30-07	175	178	0.0178		178	0.39	1.4	351	272	100	11	3	1	5	1.9	39	0.01
KL30-07	178	180.5	0.0115		115	0.1	0.8	296	301	37	3	2	1	1.5	1.3	12	0.01
KL30-07	180.5	183.2	0.0081		81	0.68	4.4	247	510	260	130	10	1	13.7	4.2	65	0.14
KL30-07	183.2	186.1	0.0067		67	0.95	5.2	213	426	340	194	9	1	16.2	5.0	100	0.11
KL30-07	186.1	189.4	0.0039		39	0.07	1.6	159	530	11	9	3	1	3.1	2.1	25	0.01
KL30-07	189.4	193	0.292		2920	0.33	13.9	870	2200	1150	23	6	4	59	2.9	23	0.11
KL30-07	193	196	0.0089		89	0.12	1	172	148	33	11	3	1	5.6	3.0	18	0.01
KL30-07	196	199	0.0127		127	0.07	1.2	236	114	50	32	4	1	10.7	2.4	20	0.01
KL30-07	199	202	0.0151		151	0.34	1.8	161	154	60	72	12	1	15.5	3.5	19	0.01
KL30-07	202	205	0.0066		66	0.1	0.6	112	95	24	101	4	1	4.3	2.4	21	0.01
KL30-07	205	208	0.0157		157	0.1	1.4	206	155	68	124	5	1	9.2	2.3	20	0.01
KL30-07	208	209.1	0.0387		387	0.12	1.6	181	72	170	250	4	1	18.1	3.1	20	0.01
KL30-07	209.1	212.3	0.0342		342	0.17	8	267	1780	130	880	26	2	7.2	11.6	36	0.01
KL30-07	212.3	215.5	0.0202		202	0.16	1.5	490	332	51	161	6	1	5.9	3.6	25	0.1
KL30-07	215.5	218.5	0.0164		164	0.12	5.8	1200	1360	30	82	19	1	7.8	9.5	30	0.01
KL30-07	218.5	221.5	0.0263		263	0.45	5.9	1440	530	62	107	20	1	30	9.8	30	0.26
KL30-07	221.5	224.5	0.0217		217	0.21	2	710	293	36	54	7	1	7.4	4.6	27	0.01
KL30-07	224.5	227.5	0.0339		339	0.51	6.1	3400	890	78	224	38	1	28	13.0	28	0.15
KL30-07	227.5	230.5	0.0208		208	0.33	2.6	1420	240	33	268	20	1	12.5	7.0	31	0.01
KL30-07	230.5	233.5	0.0178		178	0.16	1.8	1740	222	32	254	7	1	4.6	5.5	27	0.14
KL30-07	233.5	237	0.106		1060	0.31	4.2	3800	640	130	163	18	1	9.1	9.5	27	0.24
KL30-07	237	239.5	0.154		1540	1.08	52	64400	42000	230	218	70	3	44	30.5	36	0.6
KL30-07	239.5	242.5	0.139		1390	0.35	11.2	5500	1430	410	370	34	3	35	15.0	18	0.33
KL30-07	242.5	246.1	0.104		1040	0.49	6.9	2410	1130	250	212	16	1	38	7.8	26	0.44
KL30-07	246.1	249.5	8.24		82400	0.8	63	19200	9400	6800	161	285	2	360	20.0	85	4.5

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL30-07	249.5	253.3	2.2	22000	0.68	5.6	470	327	1310	220	18	5	54	71.3	95	0.21
KL30-07	253.3	256	6.31	63100	0.58	9.1	146	226	1630	178	12	4	230	77.5	67	0.19
KL30-07	256	259	2.79	27900	0.74	4.5	279	195	930	140	12	8	68	43.0	69	0.13
KL30-07	259	263	2.88	28800	1.58	4.3	373	275	1120	484	33	17	70	56.0	87	0.1
KL30-07	263	266.5	2.8	28000	1.18	6.4	850	610	1230	112	24	16	48	56.0	68	0.22
KL30-07	266.5	273.7	2.05	20500	1.24	9.2	3100	2500	700	120	23	37	26	49.0	95	0.35
KL30-07	273.7	276.2	0.44	4400	0.86	11.2	1520	3200	1010	350	27	14	36	53.0	154	0.11
KL30-07	276.2	278.5	0.34	3400	0.48	7.4	1800	322	360	570	34	40	7	81.3	162	0.2
KL30-07	278.5	281.5	0.054	540	0.86	1.5	122	131	64	518	6	96	4.4	85.0	121	0.01
KL30-07	281.5	284.5	0.52	5200	1.02	3.6	297	120	430	310	21	116	15	106.3	102	0.01
KL30-07	284.5	287.5	0.42	4200	0.86	4	970	4700	180	175	29	34	8.5	105.0	120	0.01
KL30-07	287.5	289.5	1.03	10300	0.94	6	650	660	560	102	68	31	10	126.3	138	0.01
KL30-07	289.5	292.5	1.11	11100	1.08	4.5	410	291	510	112	128	14	6.7	75.0	98	0.01
KL30-07	292.5	296.5	0.41	4100	1.42	2.4	72	82	200	32	110	2	6	61.3	139	0.01
KL30-07	296.5	299.2	0.96	9600	1.12	9.4	680	1480	420	135	54	20	7.6	92.5	118	0.01
KL30-07	299.2	302.1	0.28	2800	0.95	36	16000	5600	360	215	74	7	9.3	54.5	67	0.1
KL30-07	302.1	305.1	0.056	560	0.52	6.2	3200	820	200	90	22	6	5.8	18.0	53	0.01
KL30-07	305.1	308.3	0.0235	235	0.24	8.3	10000	7100	140	34	7	6	7.1	11.0	26	0.01
KL30-07	308.3	311.3	0.172	1720	0.52	24.6	3800	3500	200	115	12	9	25	17.0	21	0.01
KL30-07	311.3	314.3	0.067	670	1.42	62	4700	3300	370	135	14	6	36	20.9	25	0.16
KL30-07	314.3	317.3	0.39	3900	1.69	18	21800	4200	380	785	77	34	12.2	130.0	75	3.2
KL30-07	317.3	320.3	0.089	890	0.29	2.1	1020	298	110	160	10	5	2.1	10.0	26	0.15
KL30-07	320.3	323.3	0.044	440	0.99	10.6	7200	1950	490	108	28	6	22	34.5	34	0.18
KL30-07	323.3	326.5	0.115	1150	0.99	12.9	3700	1700	460	538	14	8	42	31.8	46	0.19
KL30-07	326.5	329.5	0.058	580	0.29	4.2	1110	600	200	132	4	1	4.6	10.0	28	0.01
KL30-07	329.5	333.9	0.0246	246	0.19	2	650	267	54	151	2	1	3.5	4.8	23	0.01
KL30-07	333.9	336.2	0.0068	68	0.13	0.8	217	125	17	45	2	1	3.7	4.5	24	0.01
KL30-07	336.2	338.5	0.0264	264	0.23	4.7	1880	880	62	80	26	1	5.8	29.0	24	0.01
KL30-07	338.5	341.5	0.0088	88	0.07	1.8	1790	780	30	21	4	1	1.7	13.5	19	0.01
KL30-07	341.5	344.5	0.0028	28	0.07	0.1	226	127	14	8	0.01	1	0.6	1.5	14	0.01
KL30-07	344.5	347	0.0219	219	0.25	11.3	9300	10100	65	32	12	1	10.2	105.0	27	0.01
KL30-07	347	350.1	0.0254	254	0.4	14.2	7600	10200	100	46	12	1	17	62.0	28	0.01
KL30-07	350.1	355.1	0.042	420	0.49	9.7	4600	2500	130	55	32	3	10.6	60.0	43	0.01
KL30-07	355.1	359	0.0105	105	0.07	5.5	7000	6200	61	21	2	1	8.1	26.5	16	0.01
KL30-07	359	362.5	0.076	760	0.44	60	57700	56200	120	56	12	1	60	178.8	41	0.01
KL30-07	362.5	365.5	0.0245	245	0.25	15.7	13900	14100	100	27	12	2	23	95.0	28	0.01
KL30-07	365.5	368	0.0046	46	0.09	1.8	700	550	20	21	12	1	2.5	10.5	33	0.01
KL30-07	368	371	0.0103	103	0.08	7.5	3100	4800	49	51	26	3	7.4	61.3	35	0.01
KL30-07	371	373.7	0.0102	102	0.08	6.9	4000	6400	43	43	8	3	8.3	69.0	41	0.01
KL30-07	373.7	375.9	0.0201	201	0.09	2.3	2400	1300	87	28	2	2	3.3	21.0	52	0.01
KL30-07	375.9	378.9	0.0291	291	0.09	1.7	3200	810	88	27	2	1	3.2	10.5	40	0.01
KL30-07	378.9	380.5	0.0121	121	0.2	13.8	7100	16900	110	16	2	1	24	24.5	23	0.01
KL30-07	380.5	383.2	0.0127	127	0.2	2.4	1200	910	70	16	1	1	5.8	8.0	31	0.01
KL30-07	383.2	385.9	0.0105	105	0.31	2.9	1210	960	80	17	2	1	7.3	14.0	32	0.01
KL30-07	385.9	388.3	0.0089	89	0.36	3.8	1190	1020	100	19	2	1	10.1	11.9	31	0.01
KL30-07	388.3	390	0.0085	85	0.27	4.2	2900	2500	40	15	2	1	6.8	16.5	28	0.01
KL30-07	390	392.5	0.0064	64	0.37	3.5	1320	1680	36	14	3	1	5.6	12.3	34	0.01
KL30-07	392.5	395.5	0.0055	55	0.29	2.9	1040	1550	28	12	3	1	3.6	10.5	33	0.01
KL30-07	395.5	398.5	0.0065	65	0.07	1	264	450	13	16	3	1	1.3	5.3	22	0.01
KL30-07	398.5	401.5	0.0064	64	0.03	0.8	184	370	12	12	1	1	0.9	4.8	19	0.01
KL30-07	401.5	404.2	0.0126	126	0.13	5.8	7000	5000	22	17	2	1	6.2	27.0	20	0.01
KL30-07	404.2	406.7	0.0064	64	0.05	1.8	590	540	15	36	2	1	2.5	8.3	22	0.01
KL30-07	406.7	410.5	0.0085	85	0.03	1.9	1210	440	24	48	5	1	2.2	5.5	21	0.01
KL30-07	410.5	413.5	0.004	40	0.04	1.2	296	351	13	20	3	1	1.2	4.0	21	0.01
KL30-07	413.5	416.5	0.0079	79	0.05	2.2	1060	880	35	33	6	1	1.7	7.3	22	0.01
KL30-07	416.5	419.5	0.0059	59	0.04	1.3	710	310	18	32	4	1	1.5	3.8	23	0.01
KL30-08	0	2.5	0.0095	95	0.01	0.1	59	33	5	7	0.01	1	0.6	0.7	23	0.01
KL30-08	2.5	4.8	0.0086	86	0.01	0.1	82	34	8	4	0.01	2	0.4	0.9	37	0.01
KL30-08	4.8	6.8	0.0101	101	0.01	0.1	276	67	9	6	0.01	1	0.4	2.3	28	0.01
KL30-08	6.8	8.5	0.0025	25	0.01	0.1	70	36	7	3	0.01	1	0.3	1.9	18	0.01
KL30-08	8.5	11.5	0.0035	35	0.01	0.1	93	53	8	7	0.01	1	0.4	1.0	21	0.01
KL30-08	11.5	14.5	0.0015	15	0.01	0.1	87	37	12	4	0.01	1	0.4	1.5	28	0.01
KL30-08	14.5	16.7	0.0046	46	0.01	0.1	79	30	13	4	0.01	1	0.8	1.1	30	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL30-08	16.7	18.4	0.0021		21	0.01	0.1	41	24	14	3	0.01	2	0.7	1.3	21	0.01
KL30-08	18.4	20.5	0.0056		56	0.01	0.1	239	83	12	6	0.01	1	0.9	1.5	30	0.01
KL30-08	20.5	23.5	0.0067		67	0.01	0.5	334	144	7	11	0.01	1	1	3.8	19	0.01
KL30-08	23.5	26	0.0019		19	0.06	0.1	182	119	8	5	0.01	2	0.6	2.0	20	0.01
KL30-08	26	29.1	0.0092		92	0.06	0.1	158	156	9	6	0.01	1	1	2.7	28	0.01
KL30-08	29.1	32.2	0.0081		81	0.06	3.5	750	880	17	5	1	2	3.1	8.4	32	0.01
KL30-08	32.2	35.3	0.006		60	0.01	1.2	1010	650	7	10	0.01	1	1.7	2.6	19	0.01
KL30-08	35.3	38.4	0.0269		269	0.01	0.1	53	75	5	9	0.01	1	1.5	1.3	20	0.01
KL30-08	38.4	41.4	0.0017		17	0.01	0.1	104	180	4	2	0.01	1	0.3	0.9	17	0.01
KL30-08	41.4	44.5	0.0035		35	0.01	0.1	80	131	3	4	0.01	1	0.4	0.7	18	0.01
KL30-08	44.5	47.5	0.0021		21	0.07	0.1	170	179	7	9	1	1	0.9	2.1	18	0.01
KL30-08	47.5	50.5	0.0053		53	0.05	0.1	49	70	10	9	0.01	1	0.7	1.2	14	0.01
KL30-08	50.5	53.5	0.003		30	0.01	0.1	134	315	6	2	0.01	1	0.3	1.4	16	0.01
KL30-08	53.5	56.5	0.0239		239	0.01	0.1	184	290	6	8	0.01	1	0.9	1.3	14	0.01
KL30-08	56.5	59.5	0.0149		149	0.02	0.1	740	530	15	49	1	3	1.1	2.0	27	0.01
KL30-08	59.5	62.5	0.0119		119	0.01	0.1	235	133	7	21	0.01	1	0.5	1.2	19	0.01
KL30-08	62.5	65.5	0.0012		12	0.01	0.8	112	160	5	52	1	1	0.01	0.5	8	0.01
KL30-08	65.5	68.5	0.0084		84	0.01	0.7	205	196	8	72	1	1	0.6	0.8	11	0.01
KL30-08	68.5	71.5	0.0349		349	0.01	1	620	143	16	126	1	2	0.3	1.3	22	0.01
KL30-08	71.5	74.5	0.0099		99	0.02	1.4	390	315	28	143	3	1	0.9	2.2	21	0.01
KL30-08	74.5	77.5	0.123		1230	0.04	1.6	1000	364	24	116	5	1	0.6	2.7	23	0.01
KL30-08	77.5	80.5	0.0049		49	0.09	1.4	880	540	44	99	2	1	0.9	2.0	35	0.01
KL30-08	80.5	83.5	0.0105		105	0.03	1	290	369	28	15	0.01	3	0.8	0.8	21	0.01
KL30-08	83.5	86.5	0.0201		201	0.02	0.9	420	304	16	25	1	1	1	0.6	20	0.01
KL30-08	86.5	89.5	0.0405		405	0.02	1	291	294	26	181	2	2	0.8	1.8	21	0.01
KL30-08	89.5	92.5	0.0329		329	0.03	1.6	1090	460	29	73	5	4	2	8.8	29	0.01
KL30-08	92.5	95.5	0.057		570	0.02	2.3	90	75	9	470	23	4	1.5	5.3	30	0.01
KL30-08	95.5	98.5	0.07		700	0.06	3.4	370	162	12	164	32	6	2.2	8.3	75	0.01
KL30-08	98.5	101.5	0.232		2320	0.03	3.3	142	111	9	92	16	8	1.1	15.3	105	0.01
KL30-08	101.5	104	0.048		480	0.01	0.1	78	110	9	76	1	5	0.4	9.2	126	0.01
KL30-08	104	105.4	0.0097		97	0.01	0.8	72	59	8	100	4	6	0.8	9.5	77	0.01
KL30-08	105.4	107.5	1.57		15700	0.05	25.5	2030	2300	43	127	14	17	2.1	115.0	78	0.01
KL30-08	107.5	110.5	0.85		8500	0.1	47	33900	13400	63	270	81	22	3.9	341.0	34	0.01
KL30-08	110.5	113.2	0.168		1680	0.03	3.4	260	302	40	12	4	3	4.4	9.3	12	0.01
KL30-08	113.2	115.5	0.0294		294	0.03	1	84	125	8	118	3	3	1	2.8	35	0.01
KL30-08	115.5	117.4	0.0241		241	0.04	0.9	403	280	5	35	1	2	1.1	2.3	90	0.01
KL30-08	117.4	119.5	0.0269		269	0.04	1	480	330	10	83	1	2	1.2	1.5	39	0.01
KL30-08	119.5	122.5	0.045		450	0.12	13.3	950	9900	20	407	7	2	5.9	8.3	86	0.01
KL30-08	122.5	125.5	0.319		3190	0.29	7.1	238	194	68	159	22	10	2	25.7	61	0.01
KL30-08	125.5	128.5	0.085		850	0.14	7.5	3480	3400	30	10	4	3	4.9	8.0	33	0.01
KL30-08	128.5	131.5	0.121		1210	0.12	2.7	113	63	34	6	4	2	2.1	2.1	41	0.01
KL30-08	131.5	134.5	0.418		4180	0.31	9.2	321	319	18	20	8	8	1.3	6.8	55	0.01
KL30-08	134.5	137.6	0.23		2300	0.21	6.1	570	550	12	10	2	10	1.7	5.3	78	0.01
KL30-08	137.6	140.5	0.392		3920	0.26	8.5	460	193	8	18	2	6	1.2	8.3	35	0.01
KL30-08	140.5	143.5	0.348		3480	0.31	7.8	210	323	17	12	5	8	3.3	7.5	61	0.01
KL30-08	143.5	146.5	0.227		2270	0.11	5.6	213	181	11	105	2	5	2.4	2.5	20	0.01
KL30-08	146.5	149.5	0.189		1890	0.1	4.1	112	326	12	171	3	8	1.7	2.8	48	0.01
KL30-08	149.5	152.5	0.314		3140	0.2	12	910	2230	16	240	3	10	4.5	7.0	27	0.01
KL30-08	152.5	154.1	0.0164		164	0.03	1.3	164	540	13	131	0.01	3	2.6	0.5	56	0.01
KL30-08	154.1	157.2	0.0384		384	0.05	4.8	2430	870	81	120	6	10	3.8	13.3	17	0.01
KL30-08	157.2	158.5	0.0033		33	0.03	2.2	1020	383	120	6	7	2	2.1	2.8	16	0.01
KL30-08	158.5	161.1	0.0036		36	0.05	4.7	1650	293	130	6	14	2	3.8	4.1	11	0.01
KL30-08	161.1	164.2	0.161		1610	4.65	152	35200	74000	350	30	104	5	68	62.8	38	0.19
KL30-08	164.2	165.5	0.061		610	0.25	41	22700	20800	120	18	7	2	38	34.0	18	0.14
KL30-08	165.5	167.5	0.0147		147	0.09	14.6	5400	9800	38	12	2	1	22	10.8	17	0.01
KL30-08	167.5	170.5	0.009		90	0.02	6.6	3660	3260	21	13	1	1	5.6	5.8	16	0.01
KL30-08	170.5	173.5	0.0185		185	0.06	29.5	11500	22500	52	10	0.01	1	40	8.8	20	0.1
KL30-08	173.5	176.2	0.0324		324	0.42	29.4	28100	19200	220	12	7	1	32	12.5	19	1.22
KL30-08	176.2	178.6	0.069		690	0.1	46	47800	39700	87	18	2	1	40	13.5	9	0.27
KL30-08	178.6	180.6	0.0082		82	0.08	6.8	6900	6000	51	12	1	2	7.3	8.0	10	0.12
KL30-08	180.6	183.3	0.0192		192	0.1	8.3	6800	8300	64	36	4	1	7	8.5	15	0.17
KL30-08	183.3	185.2	0.0118		118	0.04	6.7	6600	7800	12	21	0.01	2	5.7	5.5	16	0.01
KL30-08	185.2	188.3	0.0054		54	0.03	17.7	5900	4000	16	8	0.01	3	7.7	6.0	7	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL30-08	188.3	190.3	0.0116		116	0.03	39	5700	10200	16	20	0.01	1	19	8.1	13	0.01
KL30-08	190.3	193.1	0.0142		142	0.02	2.3	1770	3500	35	85	2	1	3.7	6.3	22	0.01
KL30-08	193.1	196.3	0.0156		156	0.03	1.8	3470	3150	18	122	5	1	2	12.8	21	0.01
KL30-08	196.3	197.5	0.0185		185	0.04	3.5	4880	3400	17	77	6	9	2.2	10.4	33	0.01
KL30-08	197.5	200.5	0.01		100	0.03	1.9	1310	1360	12	143	5	2	1.2	8.5	22	0.01
KL30-08	200.5	202.9	0.0256		256	0.09	11.8	9000	10300	26	312	34	2	4.2	31.7	32	0.01
KL30-08	202.9	205.7	0.0123		123	0.03	3.7	1590	2410	38	73	14	1	2	11.3	25	0.01
KL30-08	205.7	208.7	0.0094		94	0.02	1.2	950	1530	10	80	3	2	1.4	7.0	19	0.01
KL30-08	208.7	211.8	0.0024		24	0.01	1	540	730	8	21	0.01	1	1	3.8	12	0.01
KL30-08	211.8	214.9	0.0099		99	0.01	6.7	8300	8900	11	31	1	1	6.5	12.3	15	0.01
KL30-08	214.9	217.5	0.0044		44	0.01	1	379	630	5	26	2	1	0.6	3.0	12	0.01
KL30-08	217.5	219.1	0.0055		55	0.01	1.3	1670	1400	10	29	1	1	1	7.3	11	0.01
KL30-08	219.1	221.1	0.0052		52	0.01	0.9	910	1430	8	42	3	1	0.7	6.5	14	0.01
KL30-08	221.1	222.6	0.0045		45	0.01	0.5	600	630	6	94	2	1	0.4	4.3	14	0.01
KL30-08	222.6	225.6	0.0086		86	0.02	1.7	1650	1920	6	132	8	2	0.6	11.3	16	0.01
KL30-08	225.6	227.5	0.007		70	0.03	1.8	750	1250	16	41	11	1	0.7	15.8	11	0.01
KL30-08	227.5	229.7	0.0079		79	0.01	0.1	650	660	4	16	0.01	1	0.8	5.0	16	0.01
KL30-08	229.7	232.8	0.01		100	0.02	1.2	3080	2470	7	43	4	2	1.1	10.0	12	0.01
KL30-08	232.8	235.2	0.0157		157	0.04	2.2	6700	4600	11	64	2	1	3.2	13.0	10	0.01
KL30-08	235.2	237	0.0205		205	0.03	2.5	1570	1740	19	207	10	3	0.9	8.0	14	0.01
KL30-08	237	238.9	0.0092		920	0.21	13.8	12400	16800	41	278	100	2	3.1	69.8	24	0.01
KL30-08	238.9	242	0.0318		318	0.1	5.7	4410	6000	21	235	28	5	2.1	48.5	16	0.01
KL30-08	242	245	0.06		600	0.26	12.6	15600	17900	21	455	58	5	1.5	59.8	30	0.01
KL30-08	245	248.1	0.179		1790	1.06	51	28600	65600	49	680	184	2	20	301.0	38	0.01
KL30-08	248.1	251.1	0.0215		215	0.04	3.9	2080	1830	7	40	22	1	0.5	20.0	15	0.01
KL30-08	251.1	253.2	0.0119		119	0.05	2.6	1050	750	11	45	10	1	1.3	5.8	22	0.01
KL30-08	253.2	256.3	0.0093		93	0.05	4.2	1430	1600	16	48	22	1	0.8	15.8	17	0.01
KL30-08	256.3	258.1	0.0069		69	0.02	1.1	359	610	7	16	7	2	0.4	1.0	15	0.01
KL30-08	258.1	260.5	0.008		80	0.03	1.1	570	398	6	23	9	1	0.7	2.6	18	0.01
KL30-08	260.5	262	0.0074		74	0.02	4	1250	1840	9	14	12	1	1	6.3	13	0.01
KL30-08	262	263.5	0.0037		37	0.03	1.6	650	760	18	9	5	2	0.7	4.5	12	0.01
KL30-08	263.5	266.5	0.0069		69	0.02	3.6	750	1560	14	23	11	3	1.1	6.8	17	0.01
KL30-08	266.5	269.5	0.0083		83	0.02	1.7	2330	1350	13	14	3	3	1	4.0	13	0.01
KL30-08	269.5	271.8	0.026		260	0.05	6	12600	1380	29	32	18	1	1.6	14.9	21	0.01
KL30-08	271.8	274.8	0.0091		91	0.04	12.8	4410	6500	28	19	34	2	2.3	15.3	12	0.01
KL30-08	274.8	277.9	0.077		770	0.04	1.3	2840	500	42	15	8	5	1.6	3.5	19	0.01
KL30-08	277.9	281	0.104		1040	0.13	3.6	1570	940	38	25	14	5	0.9	12.0	32	0.01
KL30-08	281	283.6	0.049		490	0.07	1.6	510	119	11	7	1	1	0.4	1.8	19	0.01
KL30-08	283.6	286.4	3.83		38300	3.48	12.7	199	54	8	68	5	58	0.6	18.0	59	0.01
KL30-08	286.4	289.5	0.0385		385	0.07	0.6	3810	178	10	14	2	7	4.8	4.5	21	0.01
KL30-08	289.5	292	0.067		670	0.06	0.6	1790	200	19	9	3	6	0.8	4.8	21	0.01
KL30-08	292	293.2	0.045		450	0.04	0.1	690	372	8	7	3	2	1	2.8	16	0.01
KL30-08	293.2	295.3	0.0208		208	0.01	0.7	400	77	10	13	1	2	0.4	1.0	19	0.01
KL30-08	295.3	298															
KL30-08	298	299.5															
KL30-08	299.5	301.5															
KL30-08	301.5	304.6															
KL30-08	304.6	306.4															
KL30-08	306.4	308.5															
KL30-08	308.5	311.5															
KL30-08	311.5	314.5															
KL30-08	314.5	317.5															
KL30-08	317.5	320.5															
KL30-08	320.5	323.5															
KL30-08	323.5	326.5															
KL30-08	326.5	329.5															
KL30-08	329.5	332.5															
KL30-08	332.5	335.5															
KL30-08	335.5	338.5															
KL30-08	338.5	341.5															
KL30-08	341.5	344.5															
KL30-08	344.5	346															
KL30-08	346	347.5	1.34		13400	1.13	9.2	2600	37	1	4	1	57	0.7	9.0	16	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL30-08	347.5	350.5	2.11	21100	1.6	8.7	1610	19	2	8	2	79	0.9	9.5	15	0.01
KL30-08	350.5	353.5	0.52	5200	0.99	1.6	241	36	7	44	1	28	2	18.3	12	0.01
KL30-08	353.5	356.5	0.89	8900	1.09	2	172	25	1	81	0.01	41	0.2	15.0	12	0.01
KL30-08	356.5	359.5	0.56	5600	0.7	1.6	177	36	3	96	1	29	0.3	13.2	15	0.01
KL30-08	359.5	362.5	1.27	12700	1.13	3.8	288	30	3	50	1	47	0.3	23.0	13	0.01
KL30-08	362.5	365.5	2.76	27600	1.47	4.8	372	29	1	128	0.01	38	0.5	14.0	36	0.01
KL30-08	365.5	368.5	3.78	37800	2.03	5.6	400	20	0.01	253	0.01	41	0.3	15.0	12	0.01
KL30-08	368.5	371.5	2.15	21500	1.17	3.8	278	25	0.01	460	0.01	38	0.2	15.0	14	0.01
KL30-08	371.5	374.5	1.46	14600	0.73	2.4	163	27	0.01	34	0.01	27	0.01	9.5	13	0.01
KL30-08	374.5	377.5	0.86	8600	0.48	2.2	121	21	2	72	0.01	16	0.2	5.5	25	0.01
KL30-08	377.5	380.5	0.67	6700	0.34	2.1	106	14	1	36	0.01	13	0.2	7.0	20	0.01
KL30-08	380.5	383.5	0.95	9500	0.45	1.9	136	28	0.01	33	0.01	14	0.01	7.0	38	0.01
KL30-08	383.5	386.5	1	10000	0.56	2.2	147	24	1	53	0.01	15	0.01	7.8	33	0.01
KL30-08	386.5	388	1.29	12900	0.69	2.3	145	56	0.01	34	0.01	16	0.01	7.0	59	0.01
KL30-08	388	389.8	0.84	8400	1.01	2.7	149	17	0.01	19	0.01	18	0.01	10.7	50	0.01
KL30-08	389.8	392.5	0.56	5600	0.27	1.3	88	30	0.01	403	0.01	9	0.01	4.0	60	0.01
KL30-08	392.5	395.5	0.337	3370	0.13	1.2	54	14	0.01	151	0.01	10	0.01	2.5	54	0.01
KL30-08	395.5	397	0.392	3920	0.12	1.2	70	20	0.01	220	0.01	10	0.01	3.3	72	0.01
KL30-08	397	398.5	1.06	10600	0.57	1.7	90	13	0.01	31	0.01	16	0.01	5.5	53	0.01
KL30-08	398.5	401.5	0.91	9100	0.44	1.5	115	14	0.01	76	0.01	16	0.01	3.0	62	0.01
KL30-08	401.5	404.5	0.93	9300	0.61	1.8	177	66	0.01	70	0.01	11	0.01	6.5	78	0.01
KL30-08	404.5	407.5	1.6	16000	0.55	9.3	1450	810	46	24	11	8	17.9	14.3	90	0.01
KL30-08	407.5	410.5	3.49	34900	0.71	14	10000	1410	24	85	14	8	7.1	17.5	70	0.2
KL30-08	410.5	413.5	0.88	8800	0.41	3.9	203	89	4	33	4	11	0.8	6.0	51	0.01
KL30-08	413.5	416.5	0.8	8000	0.52	1.3	88	18	2	25	0.01	11	0.01	3.0	72	0.01
KL30-08	416.5	419.5	0.97	9700	0.71	1.8	650	62	2	93	0.01	11	0.2	5.5	80	0.01
KL30-08	419.5	422.5	1.2	12000	0.91	4.2	9800	1990	19	86	4	10	7.2	8.0	73	0.12
KL30-08	422.5	425.5	0.492	4920	0.43	0.8	43	12	1	175	0.01	6	0.2	3.3	84	0.01
KL30-08	425.5	428.5	0.84	8400	0.7	1.4	55	11	3	70	1	10	0.01	4.5	91	0.01
KL30-08	428.5	431.5	0.81	8100	0.5	1.3	68	10	5	22	0.01	7	0.01	4.0	74	0.01
KL30-08	431.5	434.5	0.8	8000	0.59	1.1	124	20	3	25	0.01	10	0.01	4.3	84	0.01
KL30-08	434.5	437.5	0.457	4570	0.33	1	54	26	3	114	0.01	8	0.01	2.8	80	0.01
KL30-08	437.5	440.5	0.61	6100	0.45	1.2	80	52	1	51	0.01	10	0.3	3.2	69	0.01
KL30-08	440.5	443.5	0.58	5800	0.67	1.1	92	15	4	26	2	9	0.01	4.0	81	0.01
KL30-08	443.5	446.5	0.7	7000	0.47	1.2	53	13	2	29	0.01	7	0.01	4.0	78	0.01
KL30-08	446.5	449.5	0.446	4460	0.35	1	63	13	2	22	0.01	7	0.01	3.1	75	0.01
KL30-08	449.5	452.5	0.54	5400	0.44	1	71	15	0.01	22	0.01	7	0.01	3.3	76	0.01
KL30-08	452.5	455.5	0.56	5600	0.36	1.3	87	15	3	23	0.01	8	0.2	3.3	66	0.01
KL30-08	455.5	458.5	0.467	4670	0.27	1	51	15	1	32	0.01	9	0.01	3.2	71	0.01
KL30-08	458.5	461.5	0.67	6700	0.42	1.3	89	21	0.01	25	0.01	13	0.2	4.3	62	0.01
KL30-08	461.5	464.5	0.74	7400	0.3	2	188	42	1	27	0.01	10	0.2	4.3	56	0.01
KL30-08	464.5	467.5	0.77	7700	0.34	1.4	99	14	1	19	0.01	16	0.3	4.5	48	0.01
KL30-08	467.5	470.5	0.447	4470	0.38	1.6	111	97	5	45	3	10	0.6	4.8	47	0.01
KL30-08	470.5	473.5	0.396	3960	0.25	1.1	77	14	1	29	0.01	10	0.01	2.5	68	0.01
KL30-08	473.5	476.5	0.63	6300	0.36	1.7	81	12	1	48	0.01	11	0.2	3.8	52	0.01
KL30-08	476.5	477.5	0.74	7400	0.43	1.7	74	16	5	17	0.01	12	0.01	4.8	41	0.01
KL30-08	477.5	482.3	0.84	8400	0.39	2.9	100	13	5	88	0.01	10	0.01	4.3	41	0.01
KL30-08	482.3	484.6	0.302	3020	0.28	1.1	72	22	2	77	0.01	6	0.01	1.8	28	0.01
KL30-08	484.6	486.1	0.65	6500	0.4	1.6	93	15	2	9	0.01	8	0.01	4.8	42	0.01
KL30-08	486.1	488	0.69	6900	0.44	1.5	89	13	3	16	0.01	12	0.2	3.2	61	0.01
KL30-08	488	489.5	0.53	5300	0.25	0.9	460	45	5	11	2	11	0.3	4.3	56	0.01
KL30-08	489.5	491.5	0.59	5900	0.22	1.5	169	28	3	10	1	4	0.2	3.8	67	0.01
KL30-08	491.5	494.5	0.59	5900	0.38	1.3	48	23	1	8	1	4	0.01	4.3	73	0.01
KL30-08	494.5	497.5	0.64	6400	0.3	1.5	86	41	2	12	1	7	0.01	4.5	52	0.01
KL30-08	497.5	500.5	0.52	5200	0.48	1.8	69	32	9	6	2	5	0.4	4.3	143	0.01
KL30-08	500.5	503.5	0.424	4240	0.11	1.3	174	63	15	6	2	3	0.3	3.1	76	0.01
KL30-08	503.5	506.5	0.56	5600	0.39	1.6	88	38	45	22	2	10	0.3	3.3	66	0.01
KL30-08	506.5	509.5	0.67	6700	0.48	2.5	208	54	5	21	2	12	0.2	4.8	59	0.01
KL30-08	509.5	512.1	0.61	6100	0.35	2.2	54	29	5	14	3	11	0.01	12.0	65	0.01
KL30-08	512.1	515.2	0.93	9300	0.78	3.3	26	13	7	16	3	11	0.5	5.0	98	0.01
KL30-08	515.2	518.3	0.8	8000	0.34	1.4	71	110	9	10	0.01	7	1.1	4.2	102	0.01
KL30-08	518.3	521.4	0.519	5190	0.27	0.8	26	26	2	13	1	4	0.6	5.5	56	0.01
KL30-08	521.4	524.5	0.356	3560	0.17	1	35	21	3	6	2	4	0.4	4.5	68	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL30-08	524.5	527.5	0.25	2500	0.1	1	114	58	28	4	3	7	0.2	4.8	54	0.01
KL30-08	527.5	530.5	0.268	2680	0.15	1.5	500	163	120	20	5	13	3.9	7.2	42	0.01
KL30-08	530.5	533.5	0.523	5230	0.3	0.8	490	53	5	21	1	6	0.01	3.0	95	0.01
KL30-08	533.5	536.5	0.499	4990	0.16	1.5	140	64	39	19	2	7	0.5	5.3	146	0.01
KL30-08	536.5	539.5	0.521	5210	0.19	1.4	145	102	30	15	3	7	0.6	3.5	49	0.01
KL30-08	539.5	542.5	0.63	6300	0.17	1.4	65	20	1	16	2	6	0.01	3.0	52	0.01
KL30-08	542.5	545.5	0.545	5450	0.15	1.2	49	20	12	13	2	14	0.5	6.1	67	0.01
KL30-08	545.5	548.5	0.78	7800	0.18	1.8	58	18	1	14	1	7	0.01	5.0	70	0.01
KL30-08	548.5	551.5	0.42	4200	0.07	0.9	172	40	2	16	1	3	0.01	2.8	54	0.01
KL30-08	551.5	554.5	0.291	2910	0.1	1	81	30	41	34	2	9	1.5	5.5	30	0.01
KL30-08	554.5	557.5	0.462	4620	0.08	1	41	19	26	32	2	8	1.9	4.9	149	0.01
KL30-08	557.5	560.5	0.152	1520	0.11	0.1	23	33	39	56	1	7	1	4.3	119	0.01
KL30-08	560.5	563.5	0.542	5420	0.3	1.4	45	20	11	28	1	9	0.2	3.1	62	0.01
KL30-08	563.5	566.5	0.64	6400	0.18	1.8	65	18	5	37	1	4	0.7	4.0	132	0.01
KL30-08	566.5	569.5	0.447	4470	0.09	1.1	28	12	6	32	1	3	0.5	3.5	114	0.01
KL30-08	569.5	572.5	0.24	2400	0.06	1	35	16	40	60	1	7	0.6	4.5	82	0.01
KL30-08	572.5	575.5	0.63	6300	0.32	1.5	108	43	36	61	5	28	1.5	14.9	108	0.01
KL30-08	575.5	578.5	0.96	9600	0.64	2.4	47	29	4	16	2	6	0.2	4.8	110	0.01
KL30-08	578.5	581.5	0.72	7200	0.43	1.7	103	56	6	30	2	10	1	4.7	96	0.01
KL30-08	581.5	584.5	0.437	4370	0.19	1.3	81	25	2	59	0.01	6	0.01	2.6	178	0.01
KL30-08	584.5	587.5	0.56	5600	0.25	1.1	32	10	2	26	0.01	6	0.01	3.8	110	0.01
KL30-08	587.5	590.5	0.77	7700	0.3	2.2	84	44	3	43	1	8	0.01	4.5	107	0.01
KL30-08	590.5	593.5	0.78	7800	0.34	2.1	108	27	4	21	1	7	0.01	5.3	88	0.01
KL30-08	593.5	596.5	0.427	4270	0.17	1.5	70	33	1	30	0.01	5	0.2	3.8	107	0.01
KL30-08	596.5	599.5	0.6	6000	0.12	1.6	56	18	2	24	0.01	4	0.2	3.8	126	0.01
KL30-08	599.5	602.5	0.26	2600	0.04	1.2	102	33	7	28	0.01	2	0.01	2.8	78	0.01
KL30-08	602.5	605.5	0.176	1760	0.08	1.3	400	231	8	42	2	7	0.4	3.8	58	0.01
KL30-08	605.5	608.5	0.098	980	0.04	0.8	98	60	8	56	1	5	0.01	4.3	41	0.01
KL30-08	608.5	611.5	0.23	2300	0.06	1.1	490	117	27	51	1	4	0.4	3.3	45	0.01
KL30-08	611.5	614.5	0.18	1800	0.06	1.1	119	92	9	62	2	4	1.3	2.7	108	0.01
KL30-08	614.5	617.5	0.158	1580	0.07	0.8	66	28	16	54	1	3	0.6	3.3	40	0.01
KL30-08	617.5	620.5	0.052	520	0.05	0.1	34	14	3	31	1	5	0.8	4.5	83	0.01
KL30-08	620.5	623.5	0.101	1010	0.05	0.1	43	18	4	29	1	3	0.4	2.5	36	0.01
KL30-08	623.5	626.5	0.3	3000	0.09	0.1	149	52	3	31	1	9	0.3	2.8	116	0.01
KL30-08	626.5	629.5	0.171	1710	0.07	1.4	150	41	41	33	3	8	1.1	8.0	85	0.01
KL30-08	629.5	632.5	0.455	4550	0.07	1.1	86	16	4	20	1	6	0.01	3.0	102	0.01
KL30-08	632.5	635.5	0.25	2500	0.04	0.1	30	8	1	18	0.01	5	0.01	2.5	135	0.01
KL30-08	635.5	638.5	0.31	3100	0.05	0.7	113	53	28	17	1	5	0.01	3.3	63	0.01
KL30-08	638.5	641.5	0.22	2200	0.06	0.1	66	50	55	11	1	5	0.01	2.3	64	0.01
KL30-08	641.5	644.5	0.24	2400	0.08	1.5	86	35	130	30	3	5	0.5	5.4	28	0.01
KL30-08	647.5	650.5	0.27	2700	0.07	1.2	110	51	3	230	1	7	0.2	2.3	67	0.01
KL30-08	650.5	653.5	0.399	3990	0.1	1.6	70	25	2	185	3	8	0.01	3.1	71	0.01
KL30-08	653.5	656.5	0.28	2800	0.05	0.9	103	18	43	59	3	7	0.2	2.5	54	0.01
KL30-08	656.5	659.5	0.3	3000	0.03	0.8	14	8	2	25	1	3	0.01	1.5	53	0.01
KL30-08	659.5	662.5	0.29	2900	0.06	1.4	180	26	8	40	1	4	0.3	3.8	48	0.01
KL30-08	662.5	665.5	0.3	3000	0.09	0.8	42	14	3	29	1	3	0.3	3.5	68	0.01
KL30-08	665.5	668.5	0.373	3730	0.08	1.3	58	18	95	37	2	5	0.7	4.0	73	0.13
KL30-08	668.5	671.5	0.204	2040	0.05	0.9	76	18	9	38	1	5	0.5	3.0	78	0.01
KL30-08	671.5	674.5	0.28	2800	0.05	1	410	69	5	52	1	4	0.4	3.3	41	0.01
KL30-08	674.5	677.5	0.22	2200	0.04	0.8	32	16	1	45	1	3	0.3	2.0	58	0.01
KL30-08	677.5	680.5	0.24	2400	0.03	0.9	121	33	3	180	0.01	5	0.7	2.8	50	0.01
KL30-08	680.5	683.5	0.22	2200	0.05	1.2	149	65	9	30	1	5	1.4	3.3	48	0.01
KL30-08	683.5	686.5	0.64	6400	0.12	1.5	27	18	5	31	2	4	1.9	5.4	61	0.01
KL30-08	686.5	689.5	0.29	2900	0.04	1.5	103	46	5	30	1	5	0.4	1.8	44	0.01
KL30-08	689.5	692.5	0.382	3820	0.06	1	32	17	7	27	1	8	0.01	2.8	96	0.01
KL30-08	692.5	695.5	0.25	2500	0.06	1.2	119	39	5	21	2	6	0.2	3.5	55	0.01
KL30-08	695.5	698.5	0.22	2200	0.09	0.1	33	10	4	26	1	7	0.7	4.3	45	0.01
KL30-08	698.5	701.5	0.418	4180	0.12	1.3	25	10	3	15	3	8	0.4	3.8	118	0.01
KL30-08	701.5	704.5	0.22	2200	0.07	1.4	215	138	8	28	2	6	0.4	3.8	54	0.01
KL30-08	704.5	707.5	0.481	4810	0.11	1.5	41	16	0.01	64	3	8	0.5	4.3	83	0.01
KL30-08	707.5	710.5	0.62	6200	0.05	2.3	145	32	21	13	2	6	0.5	3.5	80	0.01
KL30-08	710.5	713.5	0.25	2500	0.06	1.1	39	17	2	24	0.01	6	0.01	2.1	139	0.01
KL30-08	713.5	716.5	0.3	3000	0.04	1.3	45	16	1	20	1	6	0.2	3.0	139	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL30-08	716.5	719.5	0.28	2800	0.03	1.3	54	20	1	46	0.01	5	0.01	2.0	145	0.01
KL30-08	719.5	722.5	0.25	2500	0.05	1.3	74	39	2	58	1	6	0.01	2.0	131	0.01
KL30-08	722.5	725.5	0.21	2100	0.02	1.2	52	27	2	23	0.01	5	0.01	1.3	132	0.01
KL30-08	725.5	728.5	0.161	1610	0.01	0.8	42	19	1	16	0.01	4	0.2	1.8	69	0.01
KL30-08	728.5	731.5	0.168	1680	0.02	1.3	199	79	150	15	1	4	2.3	1.8	66	0.01
KL30-08	731.5	734.5	0.181	1810	0.03	0.1	150	53	1	10	1	4	0.01	1.0	70	0.01
KL30-08	734.5	737.4	0.26	2600	0.03	1.3	253	71	15	18	3	5	1.4	2.3	40	0.01
KL30-08	737.4	740.5	0.408	4080	0.04	2.2	161	49	35	21	3	7	3.3	3.1	43	0.01
KL30-08	740.5	743.5	0.24	2400	0.03	1.5	800	160	10	16	3	5	0.4	3.5	40	0.01
KL30-08	743.5	746.5	0.199	1990	0.02	0.6	182	48	9	19	2	5	0.3	3.3	51	0.01
KL30-08	746.5	749.5	0.197	1970	0.02	1	133	43	2	46	1	7	0.2	2.1	98	0.01
KL30-08	749.5	752.5	0.198	1980	0.05	0.6	53	13	2	17	1	5	0.2	2.8	93	0.01
KL30-08	752.5	755.5	0.192	1920	0.04	0.9	28	6	2	22	1	6	0.01	2.0	94	0.01
KL30-08	755.5	758.5	0.381	3810	0.04	1.1	108	34	8	45	2	9	0.3	3.8	82	0.01
KL30-08	758.5	761.5	0.497	4970	0.21	2.1	35	11	3	29	3	11	0.6	4.3	94	0.01
KL30-08	761.5	764.5	0.29	2900	0.1	0.8	26	7	2	29	1	8	0.01	2.5	97	0.01
KL30-08	764.5	767.5	0.29	2900	0.06	1.1	30	9	2	28	2	7	0.01	3.6	46	0.01
KL30-08	767.5	770.5	0.28	2800	0.04	1.1	44	14	1	51	2	8	0.3	3.5	76	0.01
KL30-08	770.5	773.5	0.196	1960	0.03	1	60	20	3	29	1	5	0.2	3.0	87	0.01
KL30-08	773.5	776.6	0.29	2900	0.02	1.3	38	18	2	27	2	4	0.01	1.7	106	0.01
KL30-08	776.6	779.5	0.76	7600	0.06	2.2	570	59	84	16	2	4	0.01	4.2	63	0.01
KL30-08	779.5	782.5	0.167	1670	0.04	0.6	132	29	2	17	2	6	0.2	2.9	91	0.01
KL30-08	782.5	785	0.52	5200	0.48	1.8	69	32	9	6	2	5	0.4	4.3	143	0.01
KL30-08	785	788.1	0.23	2300	0.03	0.8	120	40	2	32	1	4	0.01	1.7	94	0.01
KL30-08	788.1	791.2	0.22	2200	0.01	1.1	145	53	200	22	1	5	1	1.7	80	0.01
KL30-08	791.2	794.3	0.21	2100	0.01	0.9	126	72	3	16	1	5	0.01	1.7	65	0.01
KL30-08	794.3	797.4	0.148	1480	0.01	0.8	184	45	44	14	2	5	7.4	2.5	83	0.01
KL30-08	797.4	800.5	0.143	1430	0.02	0.1	93	29	91	24	2	3	1.5	1.6	51	0.01
KL30-08	800.5	803.5	0.409	4090	0.09	1.4	62	54	130	28	2	4	18	2.3	54	0.45
KL30-08	803.5	806.5	0.461	4610	0.07	1.2	86	32	1	29	1	6	0.01	1.2	68	0.01
KL30-08	806.5	809.5	0.3	3000	0.08	1	67	26	3	20	1	6	0.01	1.5	116	0.01
KL30-08	809.5	812.5	0.3	3000	0.13	2.4	205	44	9	21	0.01	7	0.8	2.0	83	0.01
KL30-08	812.5	815.5	0.2	2000	0.02	0.7	24	10	3	55	0.01	4	0.01	1.3	100	0.01
KL30-08	815.5	818.5	0.3	3000	0.07	1.4	73	24	5	24	0.01	6	0.9	1.2	66	0.01
KL30-08	818.5	821.5	0.22	2200	0.07	1	45	28	5	51	1	5	0.2	1.6	72	0.01
KL30-08	821.5	823.6	0.21	2100	0.04	0.6	56	32	25	21	0.01	6	0.6	1.2	99	0.01
KL30-08	823.6	826.7	0.189	1890	0.04	0.9	55	17	140	20	4	4	7.3	2.2	93	0.01
KL30-08	826.7	829.8	0.172	1720	0.02	0.6	31	15	1	26	0.01	4	0.01	1.6	113	0.01
KL30-08	829.8	832.9	0.25	2500	0.1	0.8	26	9	2	23	0.01	5	0.01	1.3	144	0.01
KL30-08	832.9	836	0.24	2400	0.05	0.1	35	12	4	12	1	5	0.01	1.4	93	0.01
KL30-08	836	839.1	0.129	1290	0.02	0.1	15	7	6	20	0.01	3	0.4	1.8	46	0.01
KL30-08	839.1	842.2	0.178	1780	0.03	0.1	15	7	14	25	1	4	2.1	1.9	32	0.01
KL30-08	842.2	845.4	0.23	2300	0.03	0.8	47	20	5	15	0.01	5	0.6	1.0	82	0.01
KL30-08	845.4	848.5	0.27	2700	0.04	0.7	14	11	2	18	1	3	0.2	2.4	69	0.01
KL30-08	848.5	851.5	0.119	1190	0.02	0.1	15	10	3	23	0.01	4	0.3	2.7	85	0.01
KL30-08	851.5	854.5	0.097	970	0.02	0.1	12	9	27	31	0.01	3	1.6	1.1	74	0.01
KL30-08	854.5	857.3	0.075	750	0.06	0.1	60	28	130	31	2	3	6	2.5	123	0.01
KL30-08	857.3	860.4	0.176	1760	0.02	0.8	46	19	4	42	1	4	0.01	1.8	69	0.01
KL30-08	860.4	863.5	0.187	1870	0.04	0.1	22	22	64	40	2	4	3.5	1.6	89	0.01
KL30-08	863.5	866.5	0.2	2000	0.06	0.6	34	19	8	54	1	4	0.5	1.6	100	0.01
KL30-08	866.5	869.5	0.176	1760	0.03	1	32	13	30	48	0.01	3	0.7	0.9	108	0.01
KL30-08	869.5	872.5	0.163	1630	0.04	0.9	14	11	2	23	0.01	3	0.01	0.8	160	0.01
KL30-08	872.5	875.5	0.23	2300	0.02	0.8	31	22	2	20	0.01	5	0.01	1.3	137	0.01
KL30-08	875.5	878.5	0.22	2200	0.03	0.9	17	14	46	17	0.01	6	2.5	3.1	115	0.01
KL30-08	878.5	881.5	0.22	2200	0.05	0.9	15	9	3	16	0.01	4	0.01	1.0	140	0.01
KL30-08	881.5	884.5	0.21	2100	0.02	0.7	54	26	2	13	0.01	5	0.01	1.0	107	0.01
KL30-08	884.5	887.5	0.22	2200	0.04	0.1	12	9	6	23	0.01	5	0.2	1.1	117	0.01
KL30-08	887.5	890.5	0.25	2500	0.18	0.8	20	15	5	17	0.01	4	0.01	1.1	106	0.01
KL30-08	890.5	893.5	0.105	1050	0.05	0.7	84	57	260	19	0.01	5	12.8	2.9	46	0.22
KL30-08	893.5	896.5	0.25	2500	0.06	2.4	166	21	850	18	0.01	5	26	2.4	58	0.67
KL30-08	896.5	899.5	0.159	1590	0.04	2.4	93	15	440	20	2	6	26	3.7	49	0.38
KL30-08	899.5	902.5	0.194	1940	0.02	0.5	60	28	160	68	1	12	3.9	1.9	82	0.11
KL30-08	902.5	905.5	0.188	1880	0.06	0.1	65	41	87	27	0.01	8	0.6	2.4	63	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL30-08	905.5	908.5	0.208	2080	0.02	0.6	59	26	5	34	0.01	6	0.7	2.0	84	0.01
KL30-08	908.5	911.5	0.155	1550	0.04	0.1	141	31	7	15	1	41	0.4	4.7	65	0.01
KL30-08	911.5	914.5	0.049	490	0.01	0.1	42	21	47	32	1	14	2.6	5.0	44	0.01
KL30-08	914.5	917.5	0.25	2500	0.03	0.7	89	41	4	36	1	5	0.5	2.3	73	0.01
KL30-08	917.5	920.5	0.179	1790	0.04	0.1	72	30	6	31	1	10	0.5	2.5	107	0.01
KL30-08	920.5	923.5	0.17	1700	0.14	10.3	292	550	700	25	2	19	240	5.5	50	3.35
KL30-08	923.5	926.8	0.169	1690	0.12	4.9	81	65	310	26	1	8	128	2.8	62	0.74
KL30-09	0	2	0.89	8900	0.34	1.6	43	25	35	2	20	32	1.4	35.5	85	0.01
KL30-09	2	4.5	0.93	9300	0.34	2.3	39	20	30	2	26	96	1.6	35.9	192	0.01
KL30-09	4.5	7.5	1.16	11600	0.44	2.5	40	21	21	2	42	84	1.1	42.2	181	0.01
KL30-09	7.5	9.7	0.391	3910	1.12	1.3	77	10	23	3	40	35	0.6	13.0	140	0.01
KL30-09	9.7	12.9	1.17	11700	0.44	2.9	51	18	21	3	30	56	1.3	40.0	135	0.01
KL30-09	12.9	16	0.87	8700	0.4	5.4	60	108	31	8	50	32	1.3	151.0	122	0.01
KL30-09	16	19	0.73	7300	0.4	2.6	43	44	66	10	46	38	1	52.6	201	0.01
KL30-09	19	22	0.99	9900	0.58	2.5	26	20	24	9	42	53	0.8	26.5	84	0.01
KL30-09	22	25	0.49	4900	0.44	1.5	22	19	13	8	54	37	0.7	22.5	140	0.01
KL30-09	25	28	0.57	5700	0.8	2.9	18	32	12	7	100	17	0.6	12.0	45	0.01
KL30-09	28	31	0.75	7500	0.82	2.1	22	31	10	19	70	21	0.5	13.5	40	0.01
KL30-09	31	34	0.427	4270	1.9	1.9	58	22	19	8	64	19	1.5	10.8	51	0.01
KL30-09	34	37	0.53	5300	4.42	5.6	118	27	22	20	79	25	2.8	8.5	122	0.01
KL30-09	37	38.2	0.67	6700	4.4	7.7	450	78	49	4	42	29	2.3	7.3	83	0.01
KL30-09	38.2	40	0.243	2430	1.45	3.4	124	21	14	48	101	20	0.6	15.3	42	0.01
KL30-09	40	43	0.268	2680	0.73	1	94	11	7	52	13	19	0.01	29.0	53	0.01
KL30-09	43	46	0.356	3560	0.77	1.8	76	13	14	50	12	20	1.2	12.5	126	0.01
KL30-09	46	49	0.73	7300	1.73	2.3	47	29	39	63	10	20	2.5	19.5	40	0.01
KL30-09	49	51.6	0.97	9700	2.46	2.8	55	27	12	92	9	19	1.7	15.5	113	0.01
KL30-09	51.6	53.5	1.1	11000	3.06	6.7	110	48	41	338	18	29	1.6	22.6	123	0.01
KL30-09	53.5	56.5	1.74	17400	1.79	38	73	33	23	288	62	50	1.5	51.0	138	0.01
KL30-09	56.5	59.5	1.8	18000	7.87	19	55	40	33	540	7	45	2	44.0	97	0.01
KL30-09	59.5	62.5	1.35	13500	0.96	7.1	70	18	16	420	8	18	0.9	21.3	52	0.01
KL30-09	62.5	65.5	0.57	5700	0.4	4	211	64	15	194	5	23	1	9.5	99	0.01
KL30-09	65.5	68.5	1.68	16800	1.94	26	109	36	17	152	6	35	1.8	21.0	96	0.01
KL30-09	68.5	71.5	1.91	19100	2.48	23.1	198	39	37	740	26	32	1.5	17.5	117	0.01
KL30-09	71.5	74.5	0.74	7400	0.45	4.3	68	11	16	215	3	22	0.3	8.4	63	0.01
KL30-09	74.5	77.5	1.68	16800	1.24	17.4	154	40	58	450	9	33	1.2	30.5	162	0.01
KL30-09	77.5	80.5	2.19	21900	3	15.2	74	31	35	227	9	53	1.8	48.0	97	0.01
KL30-09	80.5	83.5	1.5	15000	1.02	14.7	73	40	52	610	12	34	0.8	31.0	80	0.01
KL30-09	83.5	86.5	3.75	37500	3.8	23	85	26	30	460	50	43	1.6	19.5	67	0.01
KL30-09	86.5	89.5	7.14	71400	2.46	13.7	45	14	11	1180	2	61	0.4	40.0	141	0.01
KL30-09	89.5	92.5	1.2	12000	0.37	2	26	12	12	244	4	32	0.6	25.5	144	0.01
KL30-09	92.5	95.5	0.88	8800	0.27	1.6	26	15	6	252	4	15	0.3	20.0	103	0.01
KL30-09	95.5	98.5	1.26	12600	0.72	2.5	47	19	11	460	4	23	0.4	15.0	68	0.01
KL30-09	98.5	101.5	0.88	8800	0.43	1.7	35	10	3	315	4	24	0.2	17.0	80	0.01
KL30-09	101.5	104.5	1.06	10600	0.53	1.4	38	22	9	460	3	14	0.2	20.5	56	0.01
KL30-09	104.5	107.5	4.65	46500	0.96	10.2	19	12	8	650	7	8	0.3	21.0	64	0.01
KL30-09	107.5	108.5	3.75	37500	0.89	9.1	15	13	6	3600	9	7	0.5	23.0	131	0.01
KL30-09	108.5	110.5	0.343	3430	0.1	0.1	56	39	12	820	3	10	0.4	9.8	148	0.01
KL30-09	110.5	112	0.122	1220	0.08	0.6	7	8	4	680	2	9	0.2	8.8	76	0.01
KL30-09	112	115	0.12	1200	0.11	0.6	12	7	6	830	2	9	0.01	7.8	53	0.01
KL30-09	115	118	0.13	1300	0.11	0.1	20	10	4	540	2	10	0.01	9.8	72	0.01
KL30-09	118	121	0.457	4570	0.13	1.8	25	10	4	530	4	15	0.01	11.5	110	0.01
KL30-09	121	124	0.4	4000	0.12	0.1	24	9	2	920	1	8	0.01	10.8	80	0.01
KL30-09	124	127	0.53	5300	0.13	0.1	66	18	33	1070	2	9	0.8	12.3	72	0.01
KL30-09	127	130	0.138	1380	0.05	0.1	28	8	3	620	2	15	0.01	13.0	86	0.01
KL30-09	130	133	0.38	3800	0.15	0.7	14	8	6	910	3	16	0.01	13.7	49	0.01
KL30-09	133	136	0.175	1750	0.05	0.1	15	8	4	960	0.01	10	0.01	10.8	160	0.01
KL30-09	136	139	0.52	5200	0.1	0.7	7	6	3	550	0.01	8	0.01	9.3	110	0.01
KL30-09	139	142	0.196	1960	0.05	0.1	17	8	2	500	1	9	0.01	9.8	164	0.01
KL30-09	142	145	0.55	5500	0.14	1.2	18	7	3	590	1	14	0.01	14.5	118	0.01
KL30-09	145	148	0.265	2650	0.07	0.1	8	5	1	650	0.01	15	0.01	13.0	69	0.01
KL30-09	148	151	0.122	1220	0.07	0.1	23	12	1	480	1	10	0.01	12.5	117	0.01
KL30-09	151	154	0.58	5800	0.16	0.6	14	7	1	520	2	11	0.01	10.7	84	0.01
KL30-09	154	157	0.465	4650	0.09	0.1	8	6	0.01	385	1	23	0.01	13.8	82	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL30-09	157	160	0.3	3000	0.1	0.1	9	6	2	364	1	12	0.01	9.6	56	0.01
KL30-09	160	163	0.396	3960	0.11	0.7	40	18	0.01	410	1	13	0.01	12.0	60	0.01
KL30-09	163	166	0.53	5300	0.11	0.1	9	8	1	480	1	12	0.01	10.0	54	0.01
KL30-09	166	169	0.42	4200	0.12	0.8	10	10	1	270	1	7	0.01	8.3	67	0.01
KL30-09	169	172	0.41	4100	0.11	0.6	96	44	0.01	238	1	17	0.01	9.5	108	0.01
KL30-09	172	173.5	0.65	6500	0.21	1.6	450	135	5	290	4	12	0.4	11.5	119	0.01
KL30-09	173.5	176.5	0.67	6700	0.2	0.8	26	18	2	383	3	6	0.4	8.3	105	0.01
KL30-09	176.5	179.5	0.442	4420	0.2	1	23	11	4	207	2	10	0.01	9.5	140	0.01
KL30-09	179.5	181.5	0.376	3760	0.13	0.8	37	15	5	276	1	9	0.3	6.0	66	0.01
KL30-09	181.5	182.5	0.73	7300	0.25	3.4	34	12	4	317	4	17	0.01	10.3	84	0.01
KL30-09	182.5	185	0.8	8000	0.55	4.3	61	17	3	135	6	18	0.01	9.3	98	0.01
KL30-09	185	187	0.23	2300	0.11	0.8	27	23	2	530	2	12	0.01	8.5	94	0.01
KL30-09	187	190	0.78	7800	0.27	2.2	79	43	10	340	8	12	0.2	10.8	83	0.01
KL30-09	190	193	0.58	5800	0.8	4.8	49	16	14	200	10	13	0.01	7.8	157	0.01
KL30-09	193	195.1	0.83	8300	0.83	4.7	47	23	7	122	3	16	0.01	8.8	108	0.01
KL30-09	195.1	197.5	1.06	10600	0.5	2.4	21	18	4	314	3	24	0.01	15.5	141	0.01
KL30-09	197.5	199	2.49	24900	0.56	2.4	25	22	8	156	3	23	0.01	17.0	182	0.01
KL30-09	199	202	1.82	18200	0.69	3.8	25	18	20	49	4	26	0.01	17.5	273	0.01
KL30-09	202	205	2.3	23000	0.87	3.1	27	19	17	460	3	62	0.01	48.0	211	0.01
KL30-09	205	206.6	0.7	7000	0.4	4.4	39	15	4	142	4	18	0.01	11.8	110	0.01
KL30-09	206.6	208	0.23	2300	0.18	1.3	26	25	21	94	3	20	0.01	17.5	133	0.01
KL30-09	208	211	0.486	4860	0.2	2	53	29	9	109	2	30	0.01	13.8	223	0.01
KL30-09	211	214	0.095	950	0.08	0.1	19	16	5	312	2	20	0.01	14.0	172	0.01
KL30-09	214	217	0.455	4550	0.11	1.5	31	17	5	229	1	16	0.01	8.3	84	0.01
KL30-09	217	220	0.8	8000	0.22	2.5	37	24	5	263	2	40	0.01	17.8	170	0.01
KL30-09	220	223	0.29	2900	0.1	0.8	16	11	2	167	1	19	0.01	7.5	112	0.01
KL30-09	223	226	0.138	1380	0.05	0.1	21	10	2	232	1	14	0.01	5.0	96	0.01
KL30-09	226	229	0.365	3650	0.05	1	25	13	2	324	3	14	0.01	8.0	102	0.01
KL30-09	229	232	0.346	3460	0.12	1.1	31	18	6	251	2	11	0.01	9.0	137	0.01
KL30-09	232	235	0.185	1850	0.08	0.8	22	15	11	409	1	15	0.01	9.6	111	0.01
KL30-09	235	238	0.422	4220	0.05	0.7	24	11	0.01	356	0.01	10	0.01	7.0	80	0.01
KL30-09	238	241	0.358	3580	0.05	0.7	22	12	1	210	1	16	0.01	11.8	91	0.01
KL30-09	241	244	0.468	4680	0.17	1.2	71	27	39	208	2	19	0.6	10.3	93	0.01
KL30-09	244	247	0.385	3850	0.09	1	20	17	5	197	1	17	0.01	8.3	101	0.01
KL30-09	247	250	0.29	2900	0.08	1	18	12	5	520	2	36	0.01	11.5	83	0.01
KL30-09	250	253	0.39	3900	0.07	1.4	315	83	5	197	4	17	0.01	11.5	143	0.01
KL30-09	253	256	0.26	2600	0.06	1.1	32	20	4	385	2	19	0.01	11.8	108	0.01
KL30-09	256	259	0.37	3700	0.13	1.3	540	201	5	430	1	33	0.01	17.8	128	0.01
KL30-09	259	261.5	0.5	5000	0.1	1.2	36	33	4	79	1	23	0.01	18.7	299	0.01
KL30-09	261.5	263.5	0.71	7100	0.26	1.8	18	20	3	138	1	20	0.01	8.8	294	0.01
KL30-09	263.5	266.5	0.461	4610	0.28	3.2	53	29	4	140	3	14	0.01	14.8	134	0.01
KL30-09	266.5	268.8	0.29	2900	0.19	2.3	70	30	2	160	2	13	0.01	10.0	165	0.01
KL30-09	268.8	271	0.458	4580	0.28	3.7	37	18	2	86	3	20	0.01	17.5	164	0.01
KL30-09	271	274	0.404	4040	0.23	3	65	30	1	84	1	16	0.01	10.3	106	0.01
KL30-09	274	277	0.28	2800	0.2	1.9	68	33	2	213	1	10	0.01	16.8	53	0.01
KL30-09	277	280	0.39	3900	0.23	2.7	62	52	1	94	2	23	0.2	12.6	214	0.01
KL30-09	280	283	0.461	4610	0.28	2.9	93	72	2	123	2	24	0.2	17.5	181	0.01
KL30-09	283	286	0.25	2500	0.13	1.2	44	33	2	181	1	11	0.01	8.5	58	0.01
KL30-09	286	289	0.92	9200	0.71	7.3	110	56	12	350	5	16	0.3	18.0	139	0.01
KL30-09	289	292	0.69	6900	0.72	5.2	89	69	13	22	6	13	0.5	23.0	103	0.01
KL30-09	292	293.5	1.02	10200	0.68	7.2	232	191	40	203	7	18	0.3	17.3	150	0.01
KL30-09	293.5	296.5	0.148	1480	0.02	1.7	28	7	2	136	0.01	7	0.01	4.5	66	0.01
KL30-09	296.5	299.5	1.77	17700	0.7	5.7	184	21	48	114	5	20	0.7	18.0	151	0.01
KL30-09	299.5	302.5	1.01	10100	0.51	4.8	93	11	44	60	4	17	0.5	29.0	103	0.01
KL30-09	302.5	305.5	0.65	6500	0.37	3	92	12	15	114	3	22	0.3	26.0	162	0.01
KL30-09	305.5	308.5	0.403	4030	0.21	1.6	87	7	10	52	2	44	0.3	31.3	102	0.01
KL30-09	308.5	310.6	0.96	9600	0.56	3.1	93	8	5	121	1	68	0.01	18.3	113	0.01
KL30-09	310.6	313	0.13	1300	0.03	0.9	77	9	2	312	1	6	0.01	5.0	48	0.01
KL30-09	313	314.5	0.235	2350	0.06	1.1	121	7	3	205	1	8	0.01	3.8	71	0.01
KL30-09	314.5	317.5	1.67	16700	0.76	2.9	78	8	0.01	15	1	26	0.3	10.5	45	0.01
KL30-09	317.5	320.5	2.38	23800	1.21	4	91	6	1	125	1	30	0.2	19.5	49	0.01
KL30-09	320.5	321.5	3.01	30100	1.86	5.8	56	12	0.01	362	3	26	0.01	26.5	155	0.01
KL30-09	321.5	323.4	0.296	2960	0.06	1.2	66	9	1	226	1	6	0.01	7.2	166	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL30-09	323.4	325	0.21	2100	0.09	0.7	144	15	2	209	1	6	0.01	5.3	70	0.01
KL30-09	325	328	0.23	2300	0.12	0.9	80	18	6	188	1	4	0.7	9.1	138	0.01
KL30-09	328	329.5	0.349	3490	0.09	1	54	20	0.01	1090	1	13	0.01	7.0	235	0.01
KL30-09	329.5	332.5	0.26	2600	0.11	1.6	62	6	2	382	0.01	12	0.01	5.0	177	0.01
KL30-09	332.5	334.3	0.405	4050	0.11	1.6	66	17	1	1530	1	8	0.01	5.0	57	0.01
KL30-09	334.3	337	1.58	15800	1.01	4.7	190	22	3	450	3	53	0.9	18.5	76	0.01
KL30-09	337	338.5	0.91	9100	0.86	2.9	560	9	4	10	3	32	0.01	62.0	69	0.01
KL30-09	338.5	341.5	0.65	6500	0.6	2.2	500	11	15	28	7	21	0.3	57.0	88	0.01
KL30-09	341.5	344.5	0.53	5300	0.49	2.1	5750	10	37	17	31	27	0.7	61.0	44	0.01
KL30-09	344.5	347.5	1.53	15300	1.4	4.9	510	19	6	47	4	55	0.9	24.3	61	0.01
KL30-09	347.5	350	1.96	19600	1.63	4.5	700	16	2	104	2	45	0.9	20.0	43	0.01
KL30-09	350	351.6	1.54	15400	0.83	3.8	304	19	2	490	2	27	1.5	9.5	32	0.01
KL30-09	351.6	354.2	1.02	10200	0.47	3.8	290	43	9	630	2	20	0.5	14.0	64	0.01
KL30-09	354.2	356.5	1.49	14900	0.27	3.6	3810	27	1	255	2	19	0.6	11.5	47	0.01
KL30-09	356.5	359.5	2.83	28300	0.37	5.8	1950	17	1	23	2	28	1	13.0	38	0.01
KL30-09	359.5	362.5	3.4	34000	0.36	5	760	15	2	34	2	21	3.2	5.0	34	0.01
KL30-09	362.5	364	2.95	29500	0.34	4.6	406	15	2	30	1	30	1.1	8.0	30	0.01
KL30-09	364	366	1.92	19200	0.52	4.1	590	20	2	18	1	28	0.6	9.0	30	0.01
KL30-09	366	368	1.52	15200	0.75	4.3	374	32	6	490	1	26	0.6	13.0	42	0.01
KL30-09	368	370	0.72	7200	0.65	3.3	99	41	4	213	1	17	0.4	8.8	128	0.01
KL30-09	370	373	0.483	4830	0.33	2.5	100	30	5	350	2	21	0.3	8.0	229	0.01
KL30-09	373	376	0.467	4670	0.32	3.9	233	34	2	345	3	38	0.8	10.4	272	0.01
KL30-09	376	377.4	1.34	13400	1.45	8	238	31	19	1410	4	60	0.7	17.0	81	0.01
KL30-09	377.4	379	0.398	3980	0.24	1.5	560	21	8	290	1	57	0.7	11.0	42	0.01
KL30-09	379	382	1.32	13200	1.48	4.9	320	42	10	272	1	55	0.5	18.0	101	0.01
KL30-09	382	385	0.89	8900	0.88	3.3	226	36	8	342	2	36	0.9	10.3	87	0.01
KL30-09	385	388	0.52	5200	0.29	2.4	105	18	13	386	0.01	32	1	7.0	75	0.01
KL30-09	388	391	0.505	5050	0.52	3.1	91	18	25	450	3	37	0.7	5.0	46	0.01
KL30-09	391	394	0.95	9500	0.56	4.7	401	51	27	1360	4	67	0.6	17.5	98	0.01
KL30-09	394	397	0.353	3530	0.32	1.4	3460	51	30	115	3	51	7	16.5	23	0.01
KL30-09	397	400	1.53	15300	0.8	10.4	1120	30	5	11	9	8	0.6	67.0	50	0.01
KL30-09	400	403	0.26	2600	0.32	2.9	84	22	45	8	3	9	0.4	4.5	76	0.01
KL30-09	403	406	0.128	1280	0.27	1.9	62	16	10	36	3	8	0.2	4.0	70	0.01
KL30-09	406	409	0.395	3950	0.31	3.4	2280	36	25	10	3	19	4.1	8.0	30	0.01
KL30-09	409	412	0.41	4100	0.24	1.6	9200	17	34	7	1	51	2.4	12.0	18	0.01
KL30-09	412	415	0.214	2140	0.23	1.4	620	28	46	14	6	9	1.7	13.0	33	0.01
KL30-09	415	418	0.416	4160	0.63	3.2	490	32	35	48	85	13	1.4	16.0	22	0.01
KL30-09	418	421	0.475	4750	0.42	3.3	720	31	33	7	6	28	1	13.5	49	0.01
KL30-09	421	424	0.082	820	0.08	1.1	650	63	14	9	1	5	0.6	2.2	22	0.01
KL30-09	424	427	0.267	2670	0.25	2.8	3760	69	24	4	10	5	0.6	18.3	19	0.01
KL30-09	427	430	0.63	6300	0.57	8	14000	66	24	9	29	7	1	30.5	35	0.01
KL30-09	430	433	0.59	5900	0.46	6.6	3560	36	16	25	30	9	0.6	25.2	30	0.01
KL30-09	433	434.5	0.095	950	0.15	1.2	103	18	17	177	3	17	0.2	12.0	117	0.01
KL30-09	434.5	437.5	1.05	10500	0.64	4.6	570	16	5	24	5	9	0.3	75.0	99	0.01
KL30-09	437.5	440.5	1.52	15200	0.62	2.7	1360	29	9	22	5	42	3.3	16.0	65	0.01
KL30-09	440.5	443.5	2.38	23800	1.16	5	670	35	9	152	6	58	3	24.0	52	0.01
KL30-09	443.5	446.5	2.04	20400	1	3.4	311	13	1	250	2	48	0.4	20.0	27	0.01
KL30-09	446.5	449.5	1.02	10200	0.36	1.6	180	10	2	133	1	35	0.7	10.5	16	0.01
KL30-09	449.5	452.5	0.86	8600	0.27	1.7	5180	11	3	42	1	43	0.3	13.3	26	0.01
KL30-09	452.5	455.5	1.93	19300	0.45	3	236	10	2	26	3	39	0.5	30.0	23	0.01
KL30-09	455.5	458.5	1.6	16000	0.62	3.6	133	10	5	74	1	22	0.4	18.0	35	0.01
KL30-09	458.5	461.5	1.45	14500	0.98	2.8	165	9	2	47	1	18	0.4	16.0	36	0.01
KL30-09	461.5	464.5	1.33	13300	0.66	2.7	122	9	1	58	1	11	0.01	14.0	25	0.01
KL30-09	464.5	466.3	0.381	3810	0.23	0.7	34	8	1	32	0.01	8	0.01	7.3	103	0.01
KL30-09	466.3	468.1	0.409	4090	0.31	1.4	43	7	1	51	0.01	9	0.01	4.8	141	0.01
KL30-09	468.1	470.5	0.436	4360	0.38	1.3	53	8	1	73	0.01	10	0.01	5.0	90	0.01
KL30-09	470.5	473.5	0.2	2000	0.19	0.9	36	6	1	30	0.01	5	0.01	3.0	108	0.01
KL30-09	473.5	476.5	0.438	4380	0.37	1.7	54	7	2	39	1	8	0.01	6.0	97	0.01
KL30-09	476.5	479.5	0.46	4600	0.29	1.2	40	6	1	52	0.01	8	0.01	4.9	142	0.01
KL30-09	479.5	482.5	0.424	4240	0.29	1.2	41	6	1	63	0.01	10	0.01	4.5	120	0.01
KL30-09	482.5	485.5	1.56	15600	2.58	3.8	126	30	2	11	0.01	14	0.01	7.0	278	0.01
KL30-09	485.5	488.5	0.379	3790	0.22	0.8	34	7	1	60	0.01	7	0.01	6.3	96	0.01
KL30-09	488.5	491.5	0.46	4600	0.34	1	27	6	0.01	74	0.01	8	0.2	5.5	120	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL30-09	491.5	494.5	0.367		3670	0.27	1	60	15	2	82	2	8	0.2	6.9	102	0.01
KL30-09	494.5	497.5	0.423		4230	0.28	1	25	7	2	62	1	5	0.01	5.5	80	0.01
KL30-09	497.5	500.5	0.354		3540	0.28	0.1	21	7	2	42	1	5	0.2	6.3	98	0.01
KL30-09	500.5	503.5	0.423		4230	0.28	1	25	7	2	62	1	5	0.01	5.5	80	0.01
KL30-09	503.5	506.5	0.367		3670	0.27	1	60	15	2	82	2	8	0.2	6.9	102	0.01
KL30-09	506.5	509.5	0.46		4600	0.34	1	27	6	0.01	74	0.01	8	0.2	5.5	120	0.01
KL30-09	509.5	512.5	0.379		3790	0.22	0.8	34	7	1	60	0.01	7	0.01	6.3	96	0.01
KL30-09	512.5	515.5	0.424		4240	0.29	1.2	41	6	1	63	0.01	10	0.01	4.5	120	0.01
KL30-09	515.5	518.5	0.46		4600	0.29	1.2	40	6	1	52	0.01	8	0.01	4.9	142	0.01
KL30-09	518.5	521.5	0.438		4380	0.37	1.7	54	7	2	39	1	8	0.01	6.0	97	0.01
KL30-09	521.5	524.5	0.2		2000	0.19	0.9	36	6	1	30	0.01	5	0.01	3.0	108	0.01
KL30-09	524.5	527.5	0.436		4360	0.38	1.3	53	8	1	73	0.01	10	0.01	5.0	90	0.01
KL30-09	527.5	530.5	0.409		4090	0.31	1.4	43	7	1	51	0.01	9	0.01	4.8	141	0.01
KL30-09	530.5	533.5	0.381		3810	0.23	0.7	34	8	1	32	0.01	8	0.01	7.3	103	0.01
KL30-09	533.5	536.5	0.385		3850	0.29	1	44	8	1	33	0.01	8	0.01	5.5	102	0.01
KL30-09	536.5	539.5	0.26		2600	0.3	0.1	38	8	1	21	0.01	8	0.2	3.5	115	0.01
KL30-09	539.5	542.5	0.413		4130	0.45	1	48	7	1	36	1	8	0.01	3.3	116	0.01
KL30-09	542.5	545.5	0.25		2500	0.33	0.8	32	9	3	22	1	5	0.01	3.5	88	0.01
KL30-09	545.5	548.5	0.348		3480	0.32	0.8	34	10	2	37	0.01	7	0.01	4.0	109	0.01
KL30-09	548.5	551.5	0.26		2600	0.25	1	52	12	1	22	1	8	0.01	6.0	129	0.01
KL30-09	551.5	553.5	0.57		5700	0.38	1.8	58	11	2	40	2	11	0.01	6.4	114	0.01
KL30-09	553.5	555.5	0.83		8300	0.8	2.6	69	14	2	28	4	13	0.3	10.5	71	0.01
KL30-09	555.5	557.5	0.55		5500	0.25	1.2	39	10	1	17	0.01	9	0.01	7.1	56	0.01
KL32-01	0	3	0.0062		62	0.05	0.8	334	89	8	10	0.01	0.01	0.8	1.0	20	0.01
KL32-01	3	6	0.0027		27	0.04	0.01	158	66	5	3	0.01	0.01	0.9	0.0	24	0.01
KL32-01	6	9	0.0009		9	0.03	0.5	162	68	6	3	0.01	0.01	1	0.8	43	0.1
KL32-01	9	11.5	0.0014		14	0.05	0.01	200	61	5	3	0.01	0.01	1.9	1.0	29	0.01
KL32-01	11.5	14.6	0.0018		18	0.01	0.01	146	39	7	0.01	0.01	0.01	0.2	0.8	24	0.01
KL32-01	14.6	18	0.0017		17	0.02	0.01	203	40	8	3	0.01	0.01	1	0.8	16	0.01
KL32-01	18	21.4	0.0032		32	0.05	0.01	162	39	11	5	0.01	0.01	0.4	1.5	18	0.01
KL32-01	21.4	24	0.0023		23	0.03	1.8	226	146	7	2	0.01	0.01	0.5	1.0	14	0.01
KL32-01	24	27	0.0024		24	0.02	0.7	115	44	10	2	0.01	0.01	0.5	1.8	22	0.01
KL32-01	27	30	0.0011		11	0.04	0.01	87	34	12	4	0.01	0.01	0.01	1.3	22	0.1
KL32-01	30	33	0.0013		13	0.01	1.6	158	51	13	2	0.01	0.01	0.6	1.0	21	0.1
KL32-01	33	36	0.071		710	0.04	284	29200	22400	320	6	0.01	0.01	52	118.0	26	0.46
KL32-01	36	39	0.0022		22	0.01	2	215	139	13	3	0.01	0.01	0.8	2.3	19	0.2
KL32-01	39	42	0.001		10	0.02	0.01	56	63	7	6	0.01	0.01	0.5	0.9	21	0.1
KL32-01	42	45	0.001		10	0.03	0.8	187	390	21	3	0.01	0.01	0.7	0.8	21	0.01
KL32-01	45	48	0.0008		8	0.04	0.7	163	312	10	4	0.01	0.01	0.7	1.0	18	0.01
KL32-01	48	51	0.0021		21	0.05	1.3	404	356	15	3	0.01	0.01	0.8	2.5	20	0.1
KL32-01	51	54	0.0028		28	0.1	4.5	3500	1930	26	13	1	0.01	3.7	6.6	23	0.22
KL32-01	54	57	0.0018		18	0.06	0.7	94	920	40	16	0.01	0.01	1.1	1.3	26	0.01
KL32-01	57	60	0.0012		12	0.03	1.3	208	1020	38	5	2	0.01	1.9	6.5	22	0.01
KL32-01	60	63	0.0028		28	0.07	0.8	231	840	42	5	0.01	0.01	1.1	1.5	24	0.01
KL32-01	63	66	0.3		3000	0.14	6.9	25700	1680	120	3	8	6	3.5	36.5	47	0.28
KL32-01	66	69	0.0023		23	0.45	1.6	146	396	30	4	0.01	0.01	1.4	2.5	16	0.24
KL32-01	69	72	0.0036		36	0.37	1.8	890	1200	30	6	1	0.01	3.7	16.6	27	0.18
KL32-01	72	75	0.0015		15	0.07	0.01	142	312	28	4	0.01	0.01	2	1.5	28	0.01
KL32-01	75	78	0.0014		14	0.14	0.7	237	251	20	0.01	0.01	0.01	1.4	2.5	21	0.18
KL32-01	78	81	0.0086		86	0.1	0.01	67	93	12	6	0.01	0.01	2.1	1.5	29	0.01
KL32-01	81	84	0.0013		13	0.04	0.01	57	47	13	2	0.01	0.01	1.9	0.8	24	0.01
KL32-01	84	87	0.0011		11	0.02	0.01	41	58	11	2	0.01	0.01	0.5	0.7	35	0.01
KL32-01	87	90	0.0009		9	0.02	0.01	75	129	19	0.01	0.01	0.01	0.8	1.3	29	0.01
KL32-01	90	93	0.0011		11	0.01	0.01	87	33	11	4	0.01	0.01	0.6	1.5	26	0.01
KL32-01	93	96	0.0005		5	0.01	0.01	101	42	11	2	0.01	0.01	0.5	1.0	23	0.01
KL32-01	96	99	0.0008		8	0.01	0.01	60	30	9	2	0.01	0.01	0.5	0.0	28	0.01
KL32-01	99	102	0.001		10	0.01	0.01	97	44	8	0.01	0.01	0.01	0.3	0.6	50	0.21
KL32-01	102	105.7	0.0018		18	0.01	0.01	75	47	13	2	0.01	0.01	0.6	1.2	64	0.12
KL32-01	105.7	108	0.0065		65	0.28	6.3	3100	1490	46	3	1	5	7	7.6	35	0.27
KL32-01	108	110.3	0.0145		145	0.12	14.5	11200	6300	33	5	2	0.01	23	19.5	13	0.01
KL32-01	110.3	111.8	0.0108		108	0.23	17.6	9600	4840	46	7	0.01	0.01	21	13.2	13	0.29
KL32-01	111.8	113.35	0.069		690	0.24	69	14400	13200	260	9	0.01	0.01	88	26.5	18	0.42
KL32-01	113.35	115.5	0.0082		82	0.48	17.5	2700	5170	85	24	20	2	23	19.5	238	0.2

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL32-01	115.5	118	0.0032		32	0.18	4	910	800	13	3	0.01	2	4.6	1.2	182	0.12
KL32-01	118	121.5	0.0044		44	0.92	4.4	850	870	86	14	0.01	0.01	11.2	7.0	224	0.26
KL32-01	121.5	124.5	0.0116		116	0.07	2.6	1190	2350	34	9	1	0.01	7.4	2.5	169	0.22
KL32-01	124.5	127.5	0.01		100	0.03	52	1520	48800	33	6	11	0.01	55	11.6	260	0.17
KL32-01	127.5	130.5	0.0052		52	0.04	2.3	1760	920	17	9	2	0.01	3.7	2.0	279	0.22
KL32-01	130.5	132.5	0.0012		12	0.03	0.9	362	328	9	7	0.01	0.01	2.2	0.6	182	0.1
KL32-01	132.5	135	0.0019		19	0.31	2.1	670	750	45	11	3	0.01	5.3	2.8	220	0.15
KL32-01	135	136.9	0.0021		21	0.03	1.1	169	520	10	7	3	3	3	1.0	225	0.1
KL32-01	136.9	139.9	0.001		10	0.25	0.8	273	135	60	9	2	0.01	6.5	1.5	163	0.1
KL32-01	139.9	142.5	0.0018		18	0.13	0.6	166	69	54	5	3	0.01	4.6	2.3	110	0.01
KL32-01	142.5	145.5	0.0061		61	0.45	1.2	328	104	120	8	2	0.01	5.1	3.3	114	0.1
KL32-01	145.5	149	0.0244		244	0.66	1.1	237	131	180	12	2	0.01	3.7	2.5	136	0.1
KL32-01	149	152	0.009		90	0.54	1.4	520	156	120	18	9	0.01	5.3	4.8	152	0.1
KL32-01	152	155	0.017		170	0.74	3.3	1400	1000	160	15	22	0.01	12.9	9.6	112	0.17
KL32-01	155	158	0.0101		101	0.46	2.9	980	670	240	67	8	0.01	11.3	7.0	182	0.21
KL32-01	158	161.7	0.05		500	0.42	3.3	510	243	290	23	5	0.01	21	5.0	70	0.12
KL32-01	161.7	163.5	0.0035		35	0.19	1.3	400	230	37	13	3	0.01	4.1	3.8	41	0.1
KL32-01	163.5	166.5	0.0053		53	0.18	1.1	413	280	22	12	2	0.01	2.5	5.0	20	0.1
KL32-01	166.5	169.5	0.0015		15	0.11	0.01	237	259	19	12	0.01	0.01	2.7	3.8	21	0.01
KL32-01	169.5	172.5	0.0031		31	0.09	1.3	410	300	8	45	3	0.01	1.2	4.3	22	0.01
KL32-01	172.5	175.5	0.0038		38	0.22	3.9	1320	1210	37	44	14	0.01	6	5.7	27	0.01
KL32-01	175.5	178.3	0.0014		14	0.08	1.1	354	142	6	6	3	0.01	1.9	3.3	17	0.01
KL32-01	178.3	181.5	0.0056		56	0.11	1.8	960	325	30	21	5	0.01	4.9	6.8	24	0.1
KL32-01	181.5	184.5	0.0035		35	0.17	2.4	1160	640	21	10	6	0.01	1.9	4.3	19	0.16
KL32-01	184.5	187.5	0.0025		25	0.18	3.1	5200	3130	20	114	7	0.01	1.9	3.5	20	0.24
KL32-01	187.5	190.7	0.0022		22	0.05	1.7	430	309	8	17	4	0.01	1.2	2.5	25	0.01
KL32-01	190.7	193.5	0.001		10	0.07	0.5	213	121	8	13	3	0.01	0.6	2.5	31	0.01
KL32-01	193.5	196.5	0.0095		95	0.35	19.3	410	2140	60	29	80	0.01	7	17.0	22	0.1
KL32-01	196.5	199.2	0.007		70	0.13	1.7	800	225	30	51	6	0.01	3.6	4.5	20	0.1
KL32-01	199.2	202.5	0.0185		185	0.36	7.8	2800	1630	82	254	28	0.01	34	14.8	25	0.13
KL32-01	202.5	204	0.052		520	0.44	9.7	6200	1560	160	185	33	0.01	119	16.0	26	0.25
KL32-01	204	207	0.014		140	0.63	7.8	3100	1680	140	84	16	0.01	19.6	24.0	32	0.34
KL32-01	207	210	0.0332		332	0.15	3	1990	1570	85	66	6	0.01	9.4	5.5	20	0.13
KL32-01	210	213	0.0209		209	0.15	2	2110	770	53	151	6	0.01	10.9	5.3	28	0.14
KL32-01	213	216	0.076		760	0.28	10	6400	3940	180	77	16	0.01	35	12.0	16	0.3
KL32-01	216	219	0.321		3210	0.48	16.7	5400	3420	1050	54	25	0.01	135	13.3	16	0.3
KL32-01	219	222	0.151		1510	0.4	15.7	8200	5100	500	80	19	0.01	71	12.3	17	0.37
KL32-01	222	225	0.0345		345	0.31	10.5	7500	4100	130	163	9	0.01	17	9.0	19	0.31
KL32-01	225	228	0.0302		302	0.35	13	12600	6000	100	58	10	0.01	9.4	7.5	12	0.47
KL32-01	228	231	0.239		2390	0.22	22.7	23000	15600	40	75	13	0.01	7.1	15.5	17	0.25
KL32-01	231	233.85	11	110000	0.86	148	25900	16100	5330	22	190	0.01	126	25.0	247	0.56	
KL32-01	233.85	236.7	3.14	31400	1.21	99	37000	29000	450	68	126	2	24	31.0	155	0.25	
KL32-01	236.7	239.5	0.391	3910	0.79	53	42300	25300	310	162	57	0.01	16.7	44.0	54	0.17	
KL32-01	239.5	242.5	0.112	1120	0.35	28	16800	9200	49	265	63	0.01	6.5	46.0	37	0.01	
KL32-01	242.5	245.4	1.49	14900	1.03	75	40200	24000	810	720	288	8	34	50.8	106	0.23	
KL32-01	245.4	246.9	0.38	3800	1.99	18	6400	3800	500	99	106	3	11	57.0	341	0.1	
KL32-01	246.9	249.5	0.505	5050	1.33	10.7	3500	3020	300	34	92	19	13.1	31.3	248	0.11	
KL32-01	249.5	252.5	1.87	18700	1.39	12.7	2720	630	210	76	24	53	11.6	39.0	302	0.1	
KL32-01	252.5	255.5	2.14	21400	1.52	13.3	1470	700	170	75	43	71	19.1	22.0	269	0.11	
KL32-01	255.5	258.5	2.02	20200	1.33	9.1	690	520	160	61	29	143	6	38.8	203	0.01	
KL32-01	258.5	261.5	4.08	40800	1.08	23.4	1530	410	430	132	7	180	30	50.0	313	0.01	
KL32-01	261.5	264.5	3.59	35900	0.96	18.1	1770	450	250	119	8	88	41	41.0	337	0.11	
KL32-01	264.5	267.5	1.21	12100	0.92	16.1	880	770	320	133	66	130	58	59.2	364	0.13	
KL32-01	267.5	270.5	0.63	6300	0.61	6.3	550	321	210	17	15	192	68	56.5	339	0.1	
KL32-01	270.5	273.5	0.62	6200	1.68	11.5	1900	314	220	35	172	68	24	52.0	298	0.1	
KL32-01	273.5	276.5	0.355	3550	1.59	3.6	228	183	240	17	49	51	23	45.0	356	0.01	
KL32-01	276.5	278.2	1.06	10600	4.77	21.3	4570	1580	540	28	206	18	9.7	41.0	246	0.16	
KL32-01	278.2	279.5	0.55	5500	10.5	48	26900	7800	1080	379	98	34	61	59.0	148	0.5	
KL32-01	279.5	282.5	0.272	2720	3.65	25.1	25300	12900	550	390	60	16	25	69.5	71	1.12	
KL32-01	282.5	284	0.244	2440	3.49	24.5	44600	20200	530	440	74	13	28	87.0	69	0.4	
KL32-01	284	287	0.347	3470	1.53	17.4	14400	12800	380	600	16	20	42	29.0	39	0.42	
KL32-01	287	289	0.351	3510	1.71	31.4	34000	33400	410	910	26	33	68	64.5	44	0.51	
KL32-01	289	292	0.166	1660	1.63	29.9	18100	26700	210	1120	46	14	46	69.3	31	0.24	

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL32-01	292	297	0.0375		375	0.38	5.5	1840	1690	40	89	12	3	5.6	7.0	28	0.01
KL32-01	297	300	0.042		420	0.16	7.8	4600	9200	39	52	11	2	6.6	15.0	21	0.01
KL32-01	300	304.5	0.059		590	0.62	5.9	5400	3850	44	105	12	5	6.6	8.0	28	0.12
KL32-01	304.5	313.5	0.122		1220	0.4	7.2	3600	2140	190	84	3	22	28	13.3	26	0.1
KL32-01	313.5	315.8	0.46		4600	0.15	0.9	58	28	1	38	0.01	17	0.01	3.0	25	0.01
KL32-02	0	3	0.0019		19	0.18	2.1	1750	950	26	0.01	0.01	0.01	11.1	3.3	43	0.28
KL32-02	3	6	0.0025		25	0.06	0.7	780	283	11	2	0.01	0.01	4.3	2.2	40	0.11
KL32-02	6	9	0.0023		23	0.04	0.8	295	124	10	2	0.01	0.01	2.3	1.7	21	0.01
KL32-02	9	12	0.004		40	0.07	0.5	362	110	12	3	0.01	0.01	0.9	1.6	16	0.01
KL32-02	12	15	0.0013		13	0.06	0.01	182	37	10	2	0.01	0.01	0.8	1.8	15	0.01
KL32-02	15	18	0.0016		16	0.02	0.01	86	34	19	3	0.01	0.01	0.4	1.2	20	0.01
KL32-02	18	21	0.0017		17	0.01	2.5	231	135	8	4	0.01	0.01	0.9	3.0	16	0.01
KL32-02	21	24	0.0018		18	0.01	2	302	176	16	3	0.01	0.01	1	3.3	19	0.01
KL32-02	24	27	0.0013		13	0.01	0.01	145	274	13	3	0.01	0.01	0.5	1.0	21	0.01
KL32-02	27	30	0.0026		26	0.01	0.9	560	840	21	3	0.01	0.01	1.8	2.9	19	0.01
KL32-02	30	33	0.003		30	0.1	4	460	1830	28	21	6	0.01	3.6	5.7	22	0.01
KL32-02	33	36	0.0098		98	0.07	1	130	500	26	8	2	0.01	1.2	2.5	20	0.01
KL32-02	36	39	0.0021		21	0.24	1.1	165	395	31	4	2	0.01	1.2	1.6	19	0.01
KL32-02	39	42	0.0083		83	0.4	3.3	366	940	91	6	6	0.01	2.4	3.1	30	0.16
KL32-02	42	45	0.044		440	0.48	35	13800	7300	140	22	72	0.01	9.7	31.0	47	0.38
KL32-02	45	48	0.0018		18	0.2	0.01	125	100	18	2	0.01	0.01	0.2	1.4	22	0.01
KL32-02	48	51	0.0012		12	0.46	0.6	129	104	18	2	0.01	0.01	0.9	2.5	24	0.01
KL32-02	51	54	0.0016		16	0.48	0.7	270	176	120	2	0.01	0.01	1.1	2.2	25	0.1
KL32-02	54	57	0.0018		18	0.17	0.01	200	50	11	2	0.01	0.01	0.7	1.4	19	0.01
KL32-02	57	60	0.0008		8	0.29	0.01	49	26	12	0.01	0.01	0.01	0.01	1.2	30	0.01
KL32-02	60	63	0.0019		19	0.01	0.01	40	25	7	0.01	0.01	0.01	0.01	1.0	36	0.01
KL32-02	63	66	0.0013		13	0.01	0.01	65	31	5	0.01	0.01	0.01	0.01	1.4	28	0.01
KL32-02	66	69	0.0009		9	0.02	0.01	93	50	12	0.01	0.01	0.01	0.01	0.9	41	0.01
KL32-02	69	72	0.0051		51	0.01	0.01	77	45	7	0.01	0.01	0.01	0.01	0.9	44	0.01
KL32-02	72	75	1.28		12800	0.85	2.5	55	30	2	470	0.01	3	0.01	9.0	119	0.01
KL32-02	75	78	0.0022		22	0.03	0.01	72	40	20	2	0.01	0.01	1	1.5	106	0.01
KL32-02	78	79.5	0.047		470	0.12	4.4	2140	2400	30	13	4	0.01	12.6	9.6	23	0.14
KL32-02	79.5	81	0.0135		135	0.02	0.7	156	113	26	3	2	6	2.1	4.0	81	0.01
KL32-02	81	84	0.0385		385	0.86	41	13900	24600	200	5	32	4	33	62.5	78	0.35
KL32-02	84	87	0.044		440	0.19	9.7	8000	4500	110	14	15	0.01	28	12.5	17	0.31
KL32-02	87	90	0.045		450	0.31	57	5700	7900	120	8	110	0.01	8.3	26.0	49	0.29
KL32-02	90	93	0.148		1480	0.25	30.1	14000	8800	110	12	60	0.01	13.3	28.2	57	0.45
KL32-02	93	95.5	0.049		490	0.22	19.6	6500	7400	150	16	39	0.01	16.8	16.2	73	0.21
KL32-02	95.5	99	0.0397		397	0.11	15	885	3200	120	11	31	2	6.2	10.7	54	0.01
KL32-02	99	101.8	0.0393		393	0.06	8.2	940	3900	100	7	16	2	6.6	8.8	78	0.14
KL32-02	101.8	103	0.113		1130	0.15	27	3440	2300	380	8	191	11	34	77.0	45	0.22
KL32-02	103	105	0.0245		245	0.08	4.5	1300	1250	24	11	9	0.01	3.7	5.0	24	0.01
KL32-02	105	107.5	0.017		170	0.03	2	361	220	16	13	4	0.01	1.4	1.2	39	0.01
KL32-02	107.5	109.5	0.0119		119	0.01	0.5	179	162	22	10	3	0.01	3.4	0.7	151	0.01
KL32-02	109.5	112.5	0.045		450	0.15	5.4	2100	1340	140	25	12	3	23	7.2	17	0.01
KL32-02	112.5	115.5	0.0136		136	0.03	0.5	148	113	46	9	8	0.01	4	1.8	20	0.01
KL32-02	115.5	118.5	0.0063		63	0.04	0.01	217	114	42	4	3	0.01	3.6	1.0	83	0.01
KL32-02	118.5	121.5	0.0241		241	0.33	2.5	1270	500	110	13	6	2	6.8	3.1	38	0.19
KL32-02	121.5	123	0.0057		57	0.16	0.8	430	385	67	7	2	0.01	5.7	3.2	19	0.01
KL32-02	123	126	1.98		19800	1.1	8.4	1940	52	36	6	7	30	0.4	6.0	24	0.01
KL32-02	126	129.45	0.0118		118	0.15	3.3	1700	1040	34	20	4	0.01	6.2	5.4	17	0.01
KL32-02	129.45	132	0.0044		44	0.18	2.6	1180	480	25	5	7	3	8.5	9.8	33	0.01
KL32-02	132	135	0.02		200	0.07	2.1	1130	1610	7	7	2	0.01	4.6	3.9	21	0.01
KL32-02	135	138	0.0184		184	0.06	1.3	520	820	9	5	1	0.01	3.1	2.9	21	0.01
KL32-02	138	141	0.0144		144	0.05	1.4	1060	980	5	5	1	0.01	3.3	3.3	20	0.01
KL32-02	141	144.5	0.0194		194	0.06	1.1	342	255	8	5	2	0.01	1.7	1.9	22	0.01
KL32-02	144.5	147	0.0373		373	0.48	18.1	2730	2900	140	78	78	11	13.3	12.2	25	0.01
KL32-02	147	150.5	0.0053		53	0.05	0.6	366	377	5	5	1	2	1	2.2	21	0.01
KL32-02	150.5	153	0.044		440	0.11	4.6	1320	1350	38	12	18	2	7.2	5.0	24	0.01
KL32-02	153	156	0.057		570	0.58	25.9	3630	3800	160	96	110	14	15.2	18.9	22	0.01
KL32-02	156	158.5	0.0235		235	0.11	6.2	2810	2700	10	17	14	0.01	4.8	7.7	29	0.01
KL32-02	158.5	163	0.0192		192	0.12	6.1	5700	4600	21	21	5	0.01	7.1	9.7	31	0.01
KL32-02	163	166.5	0.0153		153	0.12	6.1	3500	2800	17	15	7	0.01	6.1	7.8	32	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL32-02	166.5	169.5	0.0226		226	0.26	14.9	10400	6700	40	11	5	0.01	25	10.5	21	0.01
KL32-02	169.5	170.8	0.0192		192	0.29	18.5	11200	7000	43	8	2	0.01	32	7.7	22	0.01
KL32-02	170.8	172	0.0298		298	0.22	8.8	4470	2700	56	33	7	0.01	22	3.3	18	0.01
KL32-02	172	173.25	0.0367		367	0.18	6.9	1910	1550	29	26	3	0.01	14.7	2.9	18	0.01
KL32-02	173.25	176	0.069		690	0.15	9.7	3760	4400	33	27	7	0.01	14.1	3.0	17	0.01
KL32-02	176	180.5	0.0197		197	0.09	4.2	770	950	14	14	7	0.01	2.6	7.6	17	0.01
KL32-02	180.5	181.75	0.0132		132	0.11	4.5	1150	940	16	22	6	0.01	8.4	4.1	22	0.01
KL32-02	181.75	184.5	0.0136		136	0.09	5.4	1590	1240	20	26	7	0.01	7.8	4.8	21	0.01
KL32-02	184.5	187.5	0.0112		112	0.09	5.7	1740	1530	22	25	5	0.01	8.6	6.0	19	0.01
KL32-02	187.5	189.9	0.0324		324	0.09	4.6	2170	3500	28	13	3	0.01	8.8	5.1	15	0.01
KL32-02	189.9	192.3	0.043		430	0.35	5.2	3180	1230	130	55	6	8	24	8.9	13	0.01
KL32-02	192.3	193.5	0.0265		265	0.26	6.9	4390	3000	84	39	4	6	17.3	9.4	15	0.01
KL32-02	193.5	196	0.0354		354	0.14	11.4	5700	3700	63	73	13	0.01	32	5.2	14	0.01
KL32-02	196	199.5	0.082		820	0.49	18.8	8600	4800	270	44	20	0.01	99	10.3	23	0.44
KL32-02	199.5	202.5	0.075		750	0.34	9.4	6800	5050	170	21	18	0.01	42	7.6	19	0.6
KL32-02	202.5	205.5	0.59		5900	0.37	5.5	152	292	140	355	7	46	6.4	15.3	180	0.19
KL32-02	205.5	208.5	0.109		1090	0.33	11.3	4390	3000	360	31	11	2	104	6.7	19	0.4
KL32-02	208.5	210	0.09		900	0.29	7.4	3890	3900	300	20	11	3	74	7.8	21	0.57
KL32-02	210	213	0.084		840	0.76	5.1	1660	1650	120	20	16	0.01	32	7.4	22	0.36
KL32-02	213	216.4	0.193		1930	3.2	12.7	7800	10000	250	47	18	5	68	12.3	25	1.48
KL32-02	216.4	217.5	0.84		8400	7.05	16.1	5100	1640	840	30	160	22	36	11.8	165	5.42
KL32-02	217.5	219	0.87		8700	3.04	11.1	212	163	210	13	32	42	17.4	15.6	51	1.23
KL32-02	219	220.5	0.8		8000	1.54	9.9	148	190	280	59	16	59	11.3	66.0	118	0.54
KL32-02	220.5	223.5	1.99		19900	1.67	15.2	880	376	230	69	8	66	8	53.0	117	0.9
KL32-02	223.5	226.55	1.56		15600	0.77	10.5	520	340	160	31	7	65	4.5	38.0	51	0.72
KL32-02	226.55	228	1.75		17500	0.37	13.1	107	73	310	426	9	34	37	41.0	209	0.44
KL32-02	228	231	1.06		10600	0.23	6.4	56	50	100	2000	4	43	3.6	23.1	276	0.16
KL32-02	231	234	1.29		12900	0.81	1.5	42	60	28	165	0.01	4	2.4	7.0	204	0.01
KL32-02	234	237.5	1.77		17700	0.96	12.9	138	166	140	30	40	48	4.3	34.0	79	0.44
KL32-02	237.5	240	1.09		10900	0.24	7	73	58	84	155	6	72	12.3	30.8	330	0.18
KL32-02	240	243	1.61		16100	0.42	12.6	246	121	140	145	28	105	40	49.5	75	0.32
KL32-02	243	246	1.02		10200	0.46	10.3	104	57	210	231	26	200	10.7	26.3	82	0.2
KL32-02	246	249	2.15		21500	0.48	16.7	163	93	160	173	23	214	12.3	47.0	280	0.2
KL32-02	249	252	2.09		20900	0.92	11.6	246	159	170	143	8	196	9.1	43.1	210	0.32
KL32-02	252	255	1.03		10300	0.77	5.3	391	331	67	121	3	54	4	14.8	186	0.26
KL32-02	255	258.5	1.03		10300	0.63	6	158	151	340	28	10	47	28	28.0	298	0.12
KL32-02	258.5	261	0.314		3140	0.52	2.6	145	600	340	48	5	72	15.3	29.8	330	0.01
KL32-02	261	264	0.287		2870	0.56	1.7	40	38	450	38	3	53	84	23.8	332	0.01
KL32-02	264	267	1.91		19100	0.58	10	100	46	2900	69	5	83	94	23.0	260	0.01
KL32-02	267	268.5	2.67		26700	0.53	19.6	96	60	160	335	22	54	12.5	23.1	293	0.13
KL32-02	268.5	274	3.82		38200	2.42	14.8	430	186	160	81	3	111	8.4	331.3	145	0.5
KL32-02	274	277.5	2.25		22500	2.64	10.2	305	130	660	24	6	102	18.1	16.8	197	0.18
KL32-02	277.5	279.3	0.65		6500	1.84	19.1	175	84	510	46	10	127	13.2	10.4	180	0.32
KL32-02	279.3	281.6	2.42		24200	1.02	8.5	76	59	230	104	4	93	9.1	14.3	252	0.15
KL32-02	281.6	285	2.3		23000	0.79	11.8	47	42	150	1170	7	54	18.9	9.8	209	0.01
KL32-02	285	288	1.25		12500	0.5	6.6	42	44	240	307	3	40	10.1	11.0	237	0.01
KL32-02	288	290.2	0.53		5300	0.37	1.2	76	38	160	242	0.01	50	6.7	15.0	107	0.01
KL32-02	290.2	292.5	0.91		9100	0.84	3.2	84	37	350	146	3	112	10.5	32.0	98	0.01
KL32-02	292.5	295.5	1.56		15600	1.86	6.8	364	100	180	40	2	97	3.7	19.4	246	0.19
KL32-02	295.5	298.5	1.51		15100	1.84	5.7	2070	1370	130	26	3	117	4.3	23.0	218	0.1
KL32-02	298.5	301.5	2.15		21500	1.31	6.7	1670	1130	110	136	2	81	2.6	18.4	96	0.39
KL32-02	301.5	304.5	2.28		22800	1.6	9.5	249	134	430	40	3	87	14.1	31.4	256	0.32
KL32-02	304.5	307.5	3.45		34500	2.88	11.4	1280	600	180	19	1	101	5.5	32.6	60	0.94
KL32-02	307.5	310.5	1.65		16500	1.41	7	3200	990	160	34	3	131	5.6	53.0	213	0.58
KL32-02	310.5	313.5	1.76		17600	1.49	6.5	550	450	110	44	2	96	3.2	26.3	53	0.35
KL32-02	313.5	316.5	1.3		13000	0.84	7.7	8200	7200	120	97	6	91	7.3	41.3	216	0.4
KL32-02	316.5	319	0.63		6300	0.63	4.9	1630	1130	160	194	5	82	2.7	45.0	72	0.15
KL32-02	319	322.5	0.73		7300	0.79	4.7	247	75	1700	63	5	96	67	42.5	231	0.27
KL32-02	322.5	325.5	1.02		10200	0.63	3.8	115	37	440	22	4	53	8.4	35.0	280	0.16
KL32-02	325.5	328.5	1.43		14300	0.84	5.2	191	95	360	12	5	15	5.8	35.4	91	0.33
KL32-02	328.5	331.4	0.71		7100	1.43	3.1	415	570	300	8	52	16	4.2	50.4	239	0.19
KL32-02	331.4	333.75	1.1		11000	1.77	6.4	3900	2600	810	75	72	6	7.1	28.3	99	0.78
KL32-02	333.75	336	0.138		1380	0.97	8.5	8800	3700	180	190	56	7	6.9	25.8	102	0.21

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL32-02	336	338	0.066		660	0.56	5.6	3190	2070	96	208	18	5	4.1	10.8	67	0.1
KL32-02	338	341	0.178		1780	0.73	6.4	5400	2070	160	138	21	7	3.4	12.0	65	0.14
KL32-02	341	344	0.025		250	0.29	1.4	840	313	61	38	4	2	1.2	5.5	35	0.01
KL32-02	344	347	0.0201		201	0.26	1.8	1040	460	29	23	3	0.01	1.4	6.3	40	0.12
KL32-02	347	350	0.0121		121	0.18	1.1	510	207	28	25	2	0.01	1.3	5.8	39	0.23
KL32-02	350	353	0.042		420	0.25	1.9	620	200	34	28	5	0.01	2.4	8.3	48	0.12
KL32-02	353	356	0.092		920	0.6	4.3	2250	1430	140	74	27	6	7.6	12.9	51	0.38
KL32-02	356	359	0.009		90	0.17	1.9	224	151	35	18	52	0.01	3.4	3.8	43	0.01
KL32-02	359	362	0.02		200	0.22	2.9	1500	1030	61	21	4	2	3.7	9.3	40	1.55
KL32-02	362	365	0.0149		149	0.16	1.4	1190	770	41	22	2	0.01	2.4	3.0	22	0.99
KL32-02	365	368	0.0208		208	0.34	0.8	470	246	62	13	2	3	6.7	3.9	28	0.43
KL32-02	368	371	0.0289		289	0.31	0.6	197	103	83	12	1	5	7.3	1.9	32	0.42
KL32-02	371	374	0.0386		386	0.22	0.7	147	90	64	13	4	6	6.3	2.2	22	0.3
KL32-02	374	377	0.074		740	0.39	1.3	760	134	93	31	4	8	5.6	4.3	50	1.46
KL32-02	377	380	0.1		1000	0.72	4.2	1860	1320	140	53	6	6	19.3	16.9	46	2.96
KL32-02	380	383	0.106		1060	1.12	10.8	3060	4500	150	62	8	6	60	28.0	39	8.78
KL32-02	383	386	0.0271		271	0.36	2.4	1950	470	79	20	4	3	12.4	9.5	29	0.42
KL32-02	386	389	0.083		830	1.26	32.2	1680	930	200	27	7	4	152	11.0	26	2.64
KL32-02	389	392	0.085		850	0.77	11	1430	900	130	23	9	3	56	8.9	28	1.55
KL32-02	392	395	0.22		2200	0.6	4.6	570	450	110	42	32	8	11.7	4.9	26	1.04
KL32-02	395	398	0.196		1960	1.21	12.7	2640	4300	170	48	25	6	73	13.5	27	3.95
KL32-02	398	401	0.062		620	0.42	7.8	5700	5400	110	37	9	3	17.1	5.6	27	2.82
KL32-02	401	404	0.197		1970	0.62	3.6	3000	2240	130	34	7	13	12.3	6.0	25	1.65
KL32-02	404	407	0.062		620	0.79	17.1	1030	600	170	25	4	2	91	5.4	21	1.86
KL32-02	407	410	0.0305		305	0.28	0.6	217	74	86	19	5	0.01	9.7	2.3	25	1.04
KL32-02	410	413	0.0176		176	0.13	0.01	146	42	120	7	1	3	2.8	1.3	27	0.4
KL32-02	413	416	0.0177		177	0.13	0.01	165	44	100	6	2	3	3	1.0	30	0.54
KL32-03	0	3	0.0025		25	0.05	1.3	690	1420	17	2	1	0.01	6.8	5.2	54	0.15
KL32-03	3	6	0.0024		24	0.02	0.5	500	274	17	2	0.01	0.01	2.6	2.7	26	0.01
KL32-03	6	9	0.0072		72	0.04	1.2	1890	650	17	6	1	0.01	2.1	5.7	47	0.01
KL32-03	9	12	0.0029		29	0.01	0.01	247	93	12	2	0.01	0.01	0.8	1.8	23	0.01
KL32-03	12	15	0.0025		25	0.01	0.01	120	45	11	3	0.01	0.01	0.8	1.3	20	0.01
KL32-03	15	18	0.0065		65	0.01	1.4	163	95	15	4	0.01	0.01	1	2.5	16	0.01
KL32-03	18	21	0.0061		61	0.01	1.2	340	268	11	3	0.01	0.01	1.2	4.5	20	0.01
KL32-03	21	24	0.0041		41	0.01	0.8	195	404	20	4	0.01	0.01	1.9	1.7	21	0.01
KL32-03	24	27	0.0152		152	0.02	10.8	3200	1950	50	33	36	0.01	6.1	12.8	25	0.12
KL32-03	27	30	0.0171		171	0.15	17.7	12200	3000	54	8	50	0.01	5.3	19.0	23	0.31
KL32-03	30	33	0.0141		141	0.06	5.6	1170	2250	30	10	10	2	3.5	8.3	21	0.01
KL32-03	33	36	0.0208		208	0.31	6	4000	1590	74	4	19	0.01	6.3	11.3	24	0.13
KL32-03	36	39	0.0063		63	0.08	0.7	420	450	29	7	1	0.01	1.5	2.5	23	0.01
KL32-03	39	42	0.0018		18	0.2	0.01	207	212	36	3	0.01	0.01	1.4	1.9	29	0.01
KL32-03	42	45	0.0024		24	0.15	0.01	197	273	70	0.01	0.01	0.01	1.1	1.4	22	0.01
KL32-03	45	48	0.0028		28	0.21	0.01	176	234	42	0.01	0.01	0.01	1.7	3.0	26	0.01
KL32-03	48	51	0.0043		43	0.16	0.01	52	46	16	0.01	0.01	0.01	0.7	1.6	24	0.01
KL32-03	51	54	0.0032		32	0.04	0.01	43	51	8	0.01	0.01	0.01	0.3	1.5	25	0.01
KL32-03	54	57	0.0025		25	0.01	0.01	78	98	11	0.01	7	0.01	0.5	2.5	22	0.01
KL32-03	57	60	0.0011		11	0.01	0.01	105	102	7	0.01	0.01	0.01	0.4	0.8	40	0.01
KL32-03	60	63	0.0016		16	0.02	0.01	154	95	24	0.01	0.01	3	0.7	0.9	45	0.01
KL32-03	63	64.5	0.003		30	0.13	1.7	800	880	40	0.01	2	3	2.8	4.1	26	0.01
KL32-03	64.5	67.5	0.0038		38	1.29	6.9	5400	1210	170	2	1	6	14.2	6.6	48	0.65
KL32-03	67.5	70.5	0.0074		74	1.06	7.8	8600	3400	170	2	1	0.01	21.8	10.2	12	0.53
KL32-03	70.5	72	0.0032		32	0.7	8.9	7400	4500	210	5	2	0.01	32	7.3	16	0.57
KL32-03	72	75	0.0022		22	0.08	0.8	680	344	14	3	0.01	0.01	1.4	1.4	20	0.01
KL32-03	75	76.4	0.0031		31	0.1	3.7	710	1160	30	4	7	0.01	5.9	4.5	51	0.11
KL32-03	76.4	78	0.0019		19	0.06	1.1	415	180	15	3	2	0.01	2.3	1.5	147	0.01
KL32-03	78	81	0.0032		32	0.07	9.9	550	2050	33	4	28	0.01	4.1	7.3	164	0.01
KL32-03	81	84	0.0026		26	0.02	4.5	214	610	47	11	13	0.01	3.4	2.1	67	0.01
KL32-03	84	87	0.0028		28	0.01	3.4	132	670	15	12	7	0.01	1.4	2.5	170	0.01
KL32-03	87	90	0.0053		53	0.03	4.6	900	2450	23	6	9	0.01	2.7	4.8	204	0.01
KL32-03	90	95.2	0.0206		206	0.06	5.5	8600	4200	66	7	7	0.01	8.3	3.0	178	0.14
KL32-03	95.2	98	0.0035		35	0.21	1.4	353	153	66	3	9	5	7.1	19.3	128	0.01
KL32-03	98	100.5	0.003		30	0.22	2	348	244	100	6	18	0.01	5.5	3.2	96	0.1
KL32-03	100.5	103.5	0.0095		95	0.09	2.1	680	392	100	8	40	0.01	9.6	4.3	65	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL32-03	103.5	106.4	0.065		650	0.05	2.5	302	212	78	7	48	0.01	4.4	9.1	43	0.01
KL32-03	106.4	109.5	0.0039		39	0.01	0.5	167	185	12	5	2	0.01	1.5	1.5	29	0.01
KL32-03	109.5	112.5	0.0018		18	0.02	0.5	308	278	11	3	1	0.01	1	1.6	18	0.01
KL32-03	112.5	115	0.175		1750	0.55	17.2	53000	16500	190	62	36	6	26	94.0	70	0.25
KL32-03	115	118.5	0.002		20	0.03	0.6	413	196	7	5	2	0.01	0.4	1.7	20	0.01
KL32-03	118.5	121.5	0.0014		14	0.03	5.5	251	470	7	4	19	0.01	1	6.1	17	0.01
KL32-03	121.5	124.5	0.0021		21	0.02	1	820	800	10	6	0.01	0.01	1	2.9	11	0.01
KL32-03	124.5	127.2	0.0027		27	0.05	1.2	820	1220	9	5	0.01	0.01	2.5	4.4	21	0.01
KL32-03	127.2	130	0.001		10	0.02	0.01	152	163	4	3	0.01	0.01	0.6	1.5	18	0.01
KL32-03	130	133.5	0.0027		27	0.03	2.1	1940	1200	8	4	3	0.01	1.6	3.6	23	0.01
KL32-03	133.5	136.5	0.0126		126	0.03	13.6	3200	12600	19	4	16	0.01	9.2	8.9	26	0.15
KL32-03	136.5	139.5	0.0044		44	0.1	1.7	159	189	47	41	4	2	1.7	4.9	21	0.01
KL32-03	139.5	142.5	0.0012		12	0.05	1.1	214	225	8	9	1	0.01	1.2	2.4	26	0.01
KL32-03	142.5	145.5	0.0005		5	0.04	0.5	163	135	5	5	0.01	0.01	0.5	1.8	23	0.01
KL32-03	145.5	148.4	0.0005		5	0.03	0.01	122	165	4	3	0.01	0.01	0.7	1.4	24	0.01
KL32-03	148.4	151.4	0.0036		36	0.03	1.3	450	840	7	6	1	0.01	5.3	1.6	25	0.01
KL32-03	151.4	154.4	0.0228		228	0.06	10.1	8600	7300	31	6	2	0.01	14.5	7.4	32	0.38
KL32-03	154.4	157.4	0.0017		17	0.04	1.6	630	730	6	7	2	0.01	1.3	2.7	26	0.01
KL32-03	157.4	160.4	0.0018		18	0.03	1.5	277	365	6	7	3	0.01	0.8	2.7	23	0.01
KL32-03	160.4	163.4	0.0026		26	0.06	1.5	540	1020	11	11	1	0.01	1.6	3.6	17	0.01
KL32-03	163.4	166.4	0.0051		51	0.05	4.1	1860	4650	15	18	1	0.01	5.6	9.6	16	0.01
KL32-03	166.4	169.4	0.0037		37	0.03	2.5	2070	1570	16	12	1	0.01	3.7	3.7	11	0.01
KL32-03	169.4	172.4	0.0015		15	0.03	2.2	183	630	6	9	3	0.01	1.4	2.5	15	0.01
KL32-03	172.4	175.4	0.0009		9	0.05	3.5	670	1130	11	9	3	0.01	3.2	3.5	15	0.01
KL32-03	175.4	178.4	0.0018		18	0.03	5.7	1330	1700	12	20	8	0.01	4.2	3.8	13	0.01
KL32-03	178.4	181.4	0.0059		59	0.05	9.6	5000	6300	22	11	3	0.01	10.9	4.7	12	0.01
KL32-03	181.4	184.4	0.0062		62	0.13	7	2080	2600	59	7	8	0.01	7.8	8.6	16	0.01
KL32-03	184.4	187.4	0.0069		69	0.04	9.6	5700	5300	17	10	6	0.01	8.9	9.4	19	0.01
KL32-03	187.4	190.4	0.0101		101	0.07	11.6	3900	4500	30	57	14	0.01	7.7	10.4	17	0.01
KL32-03	190.4	193.4	0.0191		191	0.07	18.1	7600	13300	35	29	10	0.01	16	16.0	17	0.01
KL32-03	193.4	196.4	0.0121		121	0.08	7.8	3900	3400	50	10	7	0.01	9.5	10.6	15	0.01
KL32-03	196.4	199.4	0.074		740	0.14	18.3	7900	7600	120	16	9	0.01	66	7.5	20	0.17
KL32-03	199.4	202.4	0.0312		312	0.13	9.9	13800	11000	87	24	5	2	40	11.0	13	0.01
KL32-03	202.4	205.4	0.0119		119	0.1	1.7	1130	1170	23	17	3	2	10.7	3.1	11	0.01
KL32-03	205.4	208.4	0.0261		261	0.09	3.9	1970	1260	68	26	15	3	8.4	5.8	22	0.01
KL32-03	208.4	211.4	0.027		270	0.16	6.5	2700	2700	120	19	14	2	8.3	9.1	20	0.01
KL32-03	211.4	214.4	0.052		520	0.67	5	1180	1240	130	23	7	0.01	3.8	11.7	17	0.2
KL32-03	214.4	217.8	0.102		1020	0.19	7.1	287	670	73	32	14	0.01	2	14.4	31	0.01
KL32-03	217.8	221	1.03		10300	1.4	21.2	259	279	80	15	13	35	4	40.0	148	0.01
KL32-03	221	224	1.93		19300	1.63	16.3	640	193	120	27	27	45	3.7	41.0	310	0.84
KL32-03	224	227	0.35		3500	0.19	4	142	127	340	610	5	15	3.6	12.6	311	0.3
KL32-03	227	230	0.5		5000	0.16	4.1	100	54	110	1100	3	16	2.3	16.8	140	0.19
KL32-03	230	233	0.95		9500	0.63	7.3	410	189	130	92	14	40	6.4	26.5	164	0.28
KL32-03	233	236	1.35		13500	1.29	8.6	348	139	76	93	5	23	9.2	19.5	166	0.24
KL32-03	236	239	1.01		10100	1.19	7.6	660	268	170	65	7	21	10.1	19.0	184	0.39
KL32-03	239	242	0.57		5700	0.74	4.9	730	361	110	40	9	16	8.1	21.5	56	0.22
KL32-03	242	245	0.79		7900	0.81	5.9	420	210	77	63	17	21	8.6	24.0	38	0.18
KL32-03	245	248	1.06		10600	1	7.2	231	165	120	51	21	42	6.9	22.0	32	0.01
KL32-03	248	251	0.87		8700	0.6	5.3	261	160	44	106	10	35	7.2	13.8	43	0.01
KL32-03	251	254	1.22		12200	0.76	7.5	141	67	40	268	8	18	4.3	12.2	59	0.01
KL32-03	254	257	0.79		7900	0.95	6.7	250	196	96	17	9	45	6.7	25.2	51	0.21
KL32-03	257	259.4	1.64		16400	1.64	8.7	313	62	78	258	10	54	7.8	35.5	77	0.35
KL32-03	259.4	262.4	1.65		16500	2	4.9	337	95	150	92	2	42	6.5	22.0	33	0.2
KL32-03	262.4	265.4	1.61		16100	1.79	10.2	840	82	52	9	12	22	1.5	39.3	31	0.26
KL32-03	265.4	268.4	1.8		18000	1.37	6.5	840	83	12	151	4	42	1.3	17.0	24	0.01
KL32-03	268.4	271.4	2.13		21300	2.35	7.8	640	362	300	79	10	46	7.7	29.5	112	0.54
KL32-03	271.4	274.4	2.58		25800	2.79	19.2	2840	78	45	430	7	80	1.9	25.5	200	0.84
KL32-03	274.4	277.4	3.3		33000	4.77	8.3	720	219	310	150	4	46	22	26.0	34	0.9
KL32-03	277.4	280.4	3		30000	3.05	6.3	530	47	10	280	1	52	1.4	17.0	25	0.1
KL32-03	280.4	283.4	2.49		24900	2.17	6.7	550	147	11	230	3	47	2.4	19.0	131	0.01
KL32-03	283.4	286.4	3.85		38500	2.45	13.6	610	270	210	53	43	52	5.9	26.0	254	0.41
KL32-03	286.4	289.4	3.57		35700	3.08	12.6	2400	1240	100	194	5	70	4.8	25.5	216	0.52
KL32-03	289.4	292.4	2.47		24700	3.34	8.3	640	205	150	214	2	51	3.7	18.0	238	0.28

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL32-03	292.4	295.4	2.77	27700	2.98	9.9	4840	3500	150	242	4	61	7.1	19.0	236	0.21
KL32-03	295.4	298.4	2.5	25000	2.75	9.1	850	305	390	207	8	58	6.3	30.0	293	0.16
KL32-03	298.4	301.4	4.01	40100	4.08	17.5	1740	750	160	600	5	78	7.4	22.0	302	0.14
KL32-03	301.4	304.4	2.73	27300	2.93	10.5	1420	490	290	1035	3	70	18.5	26.0	302	0.19
KL32-03	304.4	307.4	3.64	36400	2.72	12.9	112	47	400	380	7	77	6.7	28.0	310	0.19
KL32-03	307.4	310.4	4.56	45600	4.25	31.6	148	54	280	540	8	70	10.3	25.0	271	0.16
KL32-03	310.4	313.4	5.38	53800	1.57	20.2	57	25	110	550	8	61	11.8	24.0	350	0.01
KL32-03	313.4	316.4	3.48	34800	1.2	14.8	38	35	87	580	7	56	6	30.5	103	0.01
KL32-03	316.4	319.4	2.49	24900	0.95	10.7	48	34	210	590	14	37	14.4	27.0	105	0.1
KL32-03	319.4	322.4	1.91	19100	0.49	8.8	33	24	980	332	36	12	56	32.0	110	0.1
KL32-03	322.4	325.4	0.72	7200	0.3	3.4	48	41	170	560	15	16	16.8	19.5	110	0.01
KL32-03	325.4	328.4	1.62	16200	0.93	6.7	25	18	100	940	18	33	4	17.0	235	0.1
KL32-03	328.4	331.4	1.7	17000	1.5	5.1	51	35	110	1310	4	45	3.7	15.0	293	0.13
KL32-03	331.4	334.4	2.3	23000	1.13	10.6	44	22	120	1000	8	51	3.8	25.0	95	0.17
KL32-03	334.4	337.4	3.25	32500	2.97	8.3	360	41	160	117	2	65	7.9	16.0	50	0.36
KL32-03	337.4	340.4	3.05	30500	3.24	12	970	235	180	226	2	54	14.5	18.0	219	0.34
KL32-03	340.4	343.4	3.11	31100	2.82	8.1	870	378	210	560	1	70	18.8	16.0	210	0.11
KL32-03	343.4	346.4	1.37	13700	1.58	9.2	4720	1620	330	240	7	52	74	13.5	93	0.22
KL32-03	346.4	349.4	1.99	19900	2.13	5.1	510	88	100	116	4	109	10.7	11.5	214	0.01
KL32-03	349.4	352.4	3.72	37200	4.34	11.5	790	165	78	500	2	87	6.2	15.0	89	0.11
KL32-03	352.4	355.4	2.21	22100	2.24	5.2	750	99	110	242	2	80	8.7	13.5	241	0.14
KL32-03	355.4	358.4	2.14	21400	2.13	4.7	1190	245	88	320	3	78	5.2	17.0	104	0.11
KL32-03	358.4	361.4	1.49	14900	1.31	4.3	690	236	73	200	2	146	4.7	36.5	415	0.01
KL32-03	361.4	364.4	1.18	11800	1.2	5.1	1180	213	79	118	6	46	2.9	41.0	131	0.1
KL32-03	364.4	366	1.67	16700	1.44	6.2	309	460	47	97	3	65	3.2	41.5	117	0.01
KL32-03	366	369	1.2	12000	1.55	6	1110	1900	69	67	3	66	4	47.0	287	0.01
KL32-03	369	372	1.33	13300	2.63	6.4	750	1630	120	37	2	41	8.5	29.0	56	0.01
KL32-03	372	375	1.57	15700	3.05	8	920	550	160	680	2	47	9.5	18.0	189	0.01
KL32-03	375	378	0.79	7900	1.94	4.5	700	147	140	36	3	57	5.8	43.8	215	0.01
KL32-03	378	381	0.89	8900	1.81	4.4	450	183	160	250	14	62	5.3	31.0	70	0.01
KL32-03	381	384	1.35	13500	3.16	5.8	304	233	150	90	3	38	4	26.0	54	0.01
KL32-03	384	387	1.8	18000	4.58	6.1	400	170	87	10	4	54	4.6	20.5	152	0.01
KL32-03	387	390	1.31	13100	2.5	4.4	214	298	83	17	3	34	4.3	21.0	105	0.01
KL32-03	390	393	0.77	7700	1.25	2.6	184	258	110	50	2	28	5.5	26.4	175	0.01
KL32-03	393	396	0.185	1850	1.35	2.1	480	340	290	880	2	9	9.8	15.0	137	0.1
KL32-03	396	399	0.25	2500	0.94	1.9	500	248	220	770	3	11	6.5	13.0	188	0.1
KL32-03	399	402	0.255	2550	0.67	2.1	334	278	100	70	3	14	3.5	14.4	109	0.01
KL32-03	402	405	0.55	5500	0.51	4.1	372	339	74	209	1	22	2.7	11.3	44	0.13
KL32-03	405	408	0.44	4400	0.3	4.9	2400	1890	150	112	5	16	4	7.5	186	0.59
KL32-03	408	411	0.73	7300	0.39	7.1	1010	336	520	160	6	19	3.2	21.9	101	0.86
KL32-03	411	414	0.76	7600	0.23	3.5	151	68	180	354	4	14	8	8.0	207	0.18
KL32-03	414	417	0.46	4600	0.75	4.3	223	91	130	515	5	15	2.4	12.7	208	0.29
KL32-03	417	420	1.51	15100	2	11.1	401	104	320	75	3	13	1.2	13.0	59	0.66
KL32-03	420	423	3.75	37500	2.95	22.7	870	163	220	9	4	92	7.6	23.0	218	0.39
KL32-03	423	426	1.97	19700	2.93	16.3	860	158	180	4	3	70	8.7	13.5	136	0.17
KL32-03	426	429	2.4	24000	2.06	13.4	1420	690	270	14	250	117	13.3	32.0	57	0.27
KL32-03	429	432	2.25	22500	1.46	9.8	131	86	170	26	26	67	8.2	34.5	107	0.16
KL32-03	432	435	0.61	6100	2.24	9.4	550	131	250	71	40	30	2.9	34.7	231	0.3
KL32-03	435	438	0.97	9700	1.78	24.2	2010	1860	880	750	108	47	4	94.8	270	0.31
KL32-03	438	441	1.18	11800	2.6	14.5	1230	1070	420	500	76	47	4.3	49.5	198	0.36
KL32-03	441	444	1.91	19100	2.16	21.8	7900	3240	570	424	44	134	8.5	49.0	123	0.53
KL32-03	444	447	2.44	24400	3.52	18.3	3400	480	620	13	5	100	17.8	36.0	199	0.31
KL32-03	447	450	3.08	30800	4.28	23.9	4640	1190	400	7	3	112	14.7	24.5	89	0.28
KL32-03	450	453	3.59	35900	3.8	33.8	4250	1200	570	13	4	180	15.4	35.0	211	0.49
KL32-03	453	455.5	2.81	28100	3.64	35.9	9050	3280	380	12	29	127	6.5	36.0	94	0.45
KL32-03	455.5	458.5	3.08	30800	3.6	34.2	6350	2070	440	12	20	146	11.6	31.5	210	0.51
KL32-03	458.5	460	1.46	14600	1.86	29.2	24700	10700	200	184	36	57	4.3	42.0	83	0.28
KL32-03	460	463	3.42	34200	2.98	69	47800	34300	170	342	113	30	6.5	44.0	116	0.45
KL32-03	463	465	0.53	5300	0.77	12.4	8400	4360	140	560	24	18	4.3	21.7	320	0.1
KL32-03	465	467.5	0.94	9400	0.63	12.7	9500	3840	110	610	30	4	6.3	12.5	172	0.72
KL32-03	467.5	470.5	0.46	4600	0.37	1.9	243	114	90	2780	16	18	2.4	29.9	274	0.01
KL32-03	470.5	473.5	0.088	880	0.23	1.3	122	87	70	680	8	7	0.8	30.4	120	0.01
KL32-03	473.5	475.9	0.177	1770	0.22	1.2	650	70	41	630	9	10	1.6	12.3	34	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL32-03	475.9	478.8	0.39	3900	0.2	1.6	196	88	100	470	13	4	2.6	8.8	232	0.01
KL32-03	478.8	481.8	0.3	3000	0.16	1	68	37	97	325	12	3	2.4	11.0	102	0.01
KL32-03	481.8	484.3	0.41	4100	0.63	1.9	178	45	200	290	16	2	9.3	16.3	207	0.01
KL32-03	484.3	486.45	0.081	810	0.16	0.9	231	144	96	480	7	2	2.6	24.0	108	0.01
KL32-03	486.45	488.1	0.61	6100	0.18	2	103	47	300	710	7	5	10.2	12.3	104	0.01
KL32-03	488.1	491.1	0.55	5500	0.2	4.1	420	224	410	550	6	4	2.6	9.5	175	0.17
KL32-03	491.1	492	0.35	3500	0.28	3.6	720	259	460	490	5	4	7.4	9.0	47	0.44
KL32-03	492	495	0.057	570	0.26	1.7	214	145	63	975	7	7	1.1	19.7	53	0.1
KL32-03	495	498.35	0.055	550	0.12	0.01	90	52	12	264	4	4	0.5	16.0	158	0.01
KL32-03	498.35	501	0.19	1900	0.56	1.4	124	47	42	835	12	5	1.5	18.5	61	0.01
KL32-03	501	504	0.4	4000	0.5	3.2	296	118	28	1380	14	8	0.9	45.8	210	0.01
KL32-03	504	507	0.99	9900	0.7	6.6	3460	1010	300	278	31	31	5.3	82.3	87	0.34
KL32-03	507	510	0.44	4400	0.61	5.7	12200	2560	37	270	18	7	1.6	69.0	93	0.71
KL32-03	510	513	2.42	24200	1.05	5.8	185	68	710	440	9	7	11	45.5	94	0.15
KL32-03	513	516	1.52	15200	2.06	6	2310	78	86	240	47	14	3.4	55.0	113	0.28
KL32-03	516	519	1.47	14700	2.61	7.5	11100	126	44	130	150	13	2.2	78.0	394	0.53
KL32-03	519	521	0.965	9650	1.46	3.8	14300	124	58	60	62	5	3.1	40.0	373	1.12
KL32-03	521	523	2.45	24500	1.35	6.2	2570	221	1140	93	40	13	26	76.5	115	0.38
KL32-03	523	526	0.46	4600	0.4	2.5	360	152	56	1470	20	7	7.7	34.9	210	0.14
KL32-03	526	529	1.11	11100	0.42	3	228	47	200	281	14	31	4.5	47.0	305	0.18
KL32-03	529	532														
KL32-03	532	535														
KL32-03	535	538														
KL32-03	538	541														
KL32-03	541	544														
KL32-03	544	547														
KL32-03	547	550														
KL32-03	550	553														
KL32-03	553	556														
KL32-03	556	559														
KL32-03	559	562														
KL32-03	562	565														
KL32-03	565	568														
KL32-03	568	571														
KL32-03	571	574														
KL32-03	574	577														
KL32-03	577	580														
KL32-03	580	583														
KL32-03	583	586														
KL32-03	586	589														
KL32-03	589	592														
KL32-03	592	595														
KL32-03	595	598														
KL32-03	598	601														
KL32-04	0	3	0.0045	45	0.01	0.01	176	78	9	2	0.01	0.01	0.7	1.1	20	0.01
KL32-04	3	6	0.0057	57	0.01	0.01	375	112	11	4	0.01	0.01	0.8	1.5	23	0.01
KL32-04	6	9	0.0098	98	0.02	1.2	610	560	27	5	2	0.01	1.6	5.2	24	0.01
KL32-04	9	12	0.0046	46	0.02	0.01	246	132	15	3	0.01	0.01	1.1	2.9	20	0.01
KL32-04	12	15	0.025	250	0.01	5.2	2000	570	91	5	8	0.01	2.6	4.9	23	0.01
KL32-04	15	18	0.0032	32	0.09	1.4	407	710	45	4	0.01	0.01	1.5	5.4	25	0.01
KL32-04	18	21	0.0022	22	0.01	1.2	368	225	20	3	0.01	0.01	0.9	3.4	24	0.01
KL32-04	21	24	0.0025	25	0.01	0.7	261	293	18	2	0.01	2	1	2.2	24	0.01
KL32-04	24	27	0.098	980	0.07	16.5	7400	2200	320	18	24	4	8.9	18.7	20	0.23
KL32-04	27	30	0.0041	41	0.08	3	870	1790	61	9	3	0.01	3.5	7.3	21	0.01
KL32-04	30	33	0.0045	45	0.18	3.2	1220	1450	59	6	4	0.01	3	6.2	22	0.01
KL32-04	33	36	0.0202	202	0.37	10.8	3110	2010	100	15	59	0.01	6	27.5	19	0.13
KL32-04	36	39	0.003	30	0.13	1.9	640	800	43	3	1	0.01	2.3	4.4	20	0.01
KL32-04	39	42	0.0041	41	0.3	2	500	1520	80	2	0.01	0.01	2.7	9.4	25	0.12
KL32-04	42	45	0.0045	45	0.05	1.8	770	620	20	2	1	0.01	2	3.7	20	0.01
KL32-04	45	48	0.0014	14	0.02	0.01	83	98	8	0.01	0.01	0.01	0.5	2.0	21	0.01
KL32-04	48	51	0.0013	13	0.01	0.01	65	110	8	0.01	0.01	0.01	0.4	2.0	24	0.01
KL32-04	51	54	0.002	20	0.01	0.01	84	156	30	0.01	1	0.01	1	2.9	26	0.01
KL32-04	54	57	0.0159	159	0.03	0.01	96	115	75	3	1	2	3	1.2	68	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL32-04	57	60	0.017		170	0.04	2.4	970	1010	25	4	5	3	1.8	3.4	54	0.01
KL32-04	60	63	0.0216		216	0.03	3.8	1270	1470	42	4	3	2	4.1	9.9	26	0.01
KL32-04	63	66	0.0137		137	0.06	6.5	3100	2100	50	3	8	0.01	7.5	9.4	15	0.11
KL32-04	66	69	0.049		490	0.14	8.2	7500	3000	170	18	17	19	10.9	21.5	23	0.22
KL32-04	69	72	0.0363		363	0.03	4.8	1340	1840	59	7	36	2	6.2	9.3	92	0.01
KL32-04	72	75	0.0181		181	0.03	8.8	910	1020	79	9	38	0.01	5.9	38.3	21	0.01
KL32-04	75	78	0.0152		152	0.04	1.5	272	237	40	11	6	0.01	3	4.9	33	0.01
KL32-04	78	81	0.0162		162	0.02	0.01	117	173	28	6	2	0.01	1.9	1.6	35	0.01
KL32-04	81	84	0.0076		76	0.03	1.2	88	178	40	14	28	0.01	3.2	4.5	19	0.01
KL32-04	84	87	0.062		620	0.09	3.2	470	700	80	22	48	3	10.2	11.7	32	0.01
KL32-04	87	90	0.0198		198	0.1	4.8	353	580	98	9	36	0.01	7.3	6.5	30	0.01
KL32-04	90	93	0.0278		278	0.3	3.7	1530	830	120	12	10	0.01	9	8.8	36	0.01
KL32-04	93	96	0.007		70	0.01	0.01	124	190	81	11	8	0.01	7.7	3.3	19	0.01
KL32-04	96	99	0.0101		101	0.1	1.3	417	240	84	12	40	0.01	7.5	4.2	19	0.01
KL32-04	99	102	0.0186		186	0.12	12.5	5200	4800	51	8	26	0.01	5.7	12.2	18	0.1
KL32-04	102	103.2	0.0203		203	0.31	4.5	1600	1040	100	15	29	0.01	9	9.9	26	0.01
KL32-04	103.2	106	0.0106		106	0.08	3.9	1100	720	37	6	10	0.01	4	5.9	24	0.01
KL32-04	106	109	0.0097		97	0.06	8.2	2700	7000	21	8	7	0.01	6.7	9.0	20	0.01
KL32-04	109	112.2	0.0124		124	0.06	9.2	3320	5800	28	14	16	0.01	5.5	14.4	21	0.01
KL32-04	112.2	115	0.0224		224	0.02	18.8	8900	18300	15	4	11	0.01	28	15.6	18	0.1
KL32-04	115	118	0.0243		243	0.05	15.7	8800	10500	22	5	18	0.01	10	19.2	20	0.01
KL32-04	118	121	0.013		130	0.02	9.7	5800	7500	18	4	4	0.01	10.6	10.5	19	0.01
KL32-04	121	123	0.0077		77	0.01	4.1	1450	3000	8	4	4	0.01	3.8	5.0	20	0.01
KL32-04	123	126.5	0.0093		93	0.01	11.8	3400	9800	14	3	14	0.01	10.7	17.4	25	0.01
KL32-04	126.5	130	0.0069		69	0.05	13.2	2600	10600	17	2	14	0.01	11.7	9.8	23	0.01
KL32-04	130	132.5	0.0008		8	0.03	0.01	140	156	8	4	0.01	0.01	0.5	0.9	23	0.01
KL32-04	132.5	135.7	0.081		810	0.22	53.5	19200	28400	90	10	66	0.01	28.4	60.3	24	0.19
KL32-04	135.7	138.8	0.0049		49	0.02	4.4	1600	3170	8	3	11	0.01	2.5	5.3	20	0.01
KL32-04	138.8	142	0.0023		23	0.01	2	610	1070	6	4	4	0.01	1.1	2.5	18	0.01
KL32-04	142	145	0.0025		25	0.02	2.1	1410	1630	6	4	4	0.01	1.6	2.1	16	0.01
KL32-04	145	148	0.0042		42	0.04	5.3	2570	4400	12	15	9	0.01	3.8	5.0	10	0.01
KL32-04	148	151	0.0098		98	0.13	8.7	6200	6800	21	22	9	0.01	5.9	86.0	10	0.01
KL32-04	151	154	0.0016		16	0.05	1	590	700	9	13	1	0.01	0.7	2.8	10	0.01
KL32-04	154	157	0.0012		12	0.03	0.8	380	348	10	8	0.01	0.01	0.8	1.3	9	0.01
KL32-04	157	160	0.0031		31	0.01	1.4	2040	2030	8	4	0.01	0.01	1.7	1.6	9	0.01
KL32-04	160	163	0.002		20	0.02	1.2	730	860	7	3	0.01	0.01	1.2	3.1	11	0.01
KL32-04	163	166	0.0025		25	0.01	1.3	970	1350	10	5	0.01	0.01	2	2.8	12	0.01
KL32-04	166	169	0.0018		18	0.04	3.2	1520	1830	11	6	3	0.01	2.1	5.7	9	0.01
KL32-04	169	172	0.0101		101	0.12	16.3	5600	6800	46	10	1	0.01	12	7.6	12	0.1
KL32-04	172	175	0.0237		237	0.11	47.9	15200	32100	83	28	4	0.01	38	20.0	16	0.01
KL32-04	175	178	0.0125		125	0.06	10.5	4800	7600	72	21	11	0.01	8.7	13.1	13	0.01
KL32-04	178	181	0.0068		68	0.02	1	378	480	11	2	0.01	0.01	3.3	3.5	12	0.01
KL32-04	181	184	0.0104		104	0.06	5.9	7500	1860	26	28	10	2	4.5	5.4	11	0.23
KL32-04	184	187	0.0075		75	0.03	4.8	4800	3100	19	18	3	0.01	3.5	4.9	13	0.01
KL32-04	187	190	0.0214		214	0.07	6.5	7200	4900	37	25	1	0.01	6.8	6.6	12	0.01
KL32-04	190	193	0.0118		118	0.04	5.6	3840	4800	40	16	2	2	4	7.9	13	0.01
KL32-04	193	196	0.0339		339	0.14	6.2	4000	5110	82	17	3	0.01	4.9	13.2	18	0.01
KL32-04	196	199	0.0156		156	0.08	3.5	2120	1600	65	46	7	4	2.8	7.3	26	0.01
KL32-04	199	202	0.0122		122	0.04	3.1	960	830	28	35	12	2	0.9	10.7	16	0.01
KL32-04	202	205	0.32		3200	0.36	8.7	9300	710	41	518	50	3	2	12.7	13	0.01
KL32-04	205	208	0.0147		147	0.05	1.6	113	174	20	62	10	2	0.5	4.5	12	0.01
KL32-04	208	211	0.028		280	0.09	1.2	660	149	36	30	18	0.01	0.6	3.1	13	0.01
KL32-04	211	214	0.0345		345	0.12	2.4	1020	540	96	29	24	3	1.4	6.3	11	0.21
KL32-04	214	217	0.085		850	0.15	2.2	1900	382	73	38	20	2	1.5	6.7	14	0.21
KL32-04	217	219.2	0.078		780	0.13	3.4	2800	1630	53	47	17	2	1	4.8	10	0.2
KL32-04	219.2	220.1	1.27		12700	2.92	45.7	5500	2500	69	258	82	37	2.4	32.3	51	0.01
KL32-04	220.1	223	1.03		10300	1.07	23.5	730	162	58	35	20	35	1.9	26.5	49	0.01
KL32-04	223	226	0.42		4200	0.56	11.3	313	97	43	994	42	12	2.8	14.4	85	0.01
KL32-04	226	229	0.266		2660	0.19	4.9	128	71	25	2320	30	12	2.7	6.2	87	0.01
KL32-04	229	232	0.395		3950	0.38	9.2	145	117	17	1460	40	16	1.3	8.3	124	0.01
KL32-04	232	235	0.264		2640	0.24	12.9	194	600	11	430	55	6	1	4.6	54	0.01
KL32-04	235	238	0.58		5800	0.51	27.5	357	770	33	209	134	25	2.3	21.9	110	0.01
KL32-04	238	241	0.73		7300	0.26	15.6	282	101	33	232	12	20	2.4	14.8	42	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL32-04	241	244	0.54	5400	0.23	10.6	73	27	38	64	13	11	1.8	8.2	44	0.01
KL32-04	244	247	0.5	5000	0.29	9.5	250	68	83	33	10	43	1.3	18.0	45	0.01
KL32-04	247	250	1.29	12900	0.92	23.9	3100	1100	1130	176	9	18	200	16.3	100	0.54
KL32-04	250	253	0.09	900	0.27	3	430	232	62	59	4	3	6.3	14.3	80	0.15
KL32-04	253	256	0.0335	335	0.1	2.2	120	48	18	460	8	4	3	10.9	18	0.01
KL32-04	256	258	0.17	1700	0.27	5.2	320	93	28	450	7	5	1.9	13.3	39	0.01
KL32-04	258	261	0.161	1610	1.19	5.3	208	85	39	74	19	12	3.6	7.2	48	0.01
KL32-04	261	264	0.379	3790	0.53	2.5	158	64	32	4	30	15	1.8	8.9	70	0.01
KL32-04	264	267	0.85	8500	1.35	6.3	272	154	26	11	260	15	3	7.0	63	0.01
KL32-04	267	270	0.67	6700	1	2.5	680	198	81	8	19	16	2.7	16.8	52	0.12
KL32-04	270	273	0.478	4780	0.66	1.7	121	111	33	0.01	4	14	2.3	9.9	59	0.01
KL32-04	273	276	0.95	9500	1.34	3.8	146	54	81	2	16	16	2.3	1.5	67	0.01
KL32-04	276	279	0.97	9700	2.05	3.7	510	83	80	10	26	24	4.6	4.2	66	0.18
KL32-04	279	282	2.18	21800	2	7.5	96	26	21	6	2	36	4.6	25.3	45	0.01
KL32-04	282	285	1.56	15600	1.36	3.7	110	30	15	4	2	43	1.1	17.3	55	0.01
KL32-04	285	288	2.28	22800	1.13	6.4	680	133	51	34	2	56	1.3	20.7	88	0.23
KL32-04	288	291	2.29	22900	1.94	5.2	450	107	360	30	2	52	5.9	20.7	98	0.17
KL32-04	291	294	2	20000	1.13	4.8	239	76	60	3	2	47	9.3	15.5	84	0.17
KL32-04	294	297	2.79	27900	2.27	7.3	140	34	22	8	1	37	1.1	22.5	56	0.14
KL32-04	297	300	2.68	26800	2.25	9.3	630	134	69	3	2	48	10.8	27.5	84	0.22
KL32-04	300	303	3.5	35000	2.77	8.9	359	66	28	21	1	49	0.01	36.0	95	0.18
KL32-04	303	306	2.31	23100	0.56	4.3	2400	580	960	540	4	56	1.2	23.5	55	1.1
KL32-04	306	309	0.57	5700	0.23	1.6	940	198	150	120	3	30	0.5	20.1	91	0.86
KL32-04	309	312	0.89	8900	0.35	3	1310	265	520	56	3	38	8.5	16.5	83	1.3
KL32-04	312	315	1.27	12700	0.59	2.4	250	78	170	342	1	19	0.9	12.5	64	0.28
KL32-04	315	318	0.311	3110	0.17	1.1	800	229	210	399	1	40	4.4	26.2	436	0.25
KL32-04	318	321	1.75	17500	0.36	2.9	600	169	540	157	2	34	3.4	14.0	92	0.51
KL32-04	321	324	1.26	12600	0.2	2.7	110	39	20	227	1	42	0.3	32.5	213	0.12
KL32-04	324	327	1.31	13100	0.2	3.2	173	88	220	520	0.01	47	0.4	21.5	195	0.22
KL32-04	327	330	1.15	11500	0.3	3.4	146	65	84	830	0.01	94	0.2	20.5	200	0.13
KL32-04	330	333	0.86	8600	0.28	2.1	190	89	36	195	0.01	68	0.2	14.8	194	0.1
KL32-04	333	336	1.12	11200	0.42	2.2	324	240	91	373	0.01	54	0.8	9.3	196	0.11
KL32-04	336	339	1.03	10300	0.41	2.1	161	347	39	501	1	45	0.8	10.8	195	0.11
KL32-04	339	342	1.3	13000	0.48	2.5	1450	1260	720	520	0.01	48	22	11.5	144	0.58
KL32-04	342	345	1.21	12100	0.55	2.1	570	420	290	830	1	45	2.5	16.0	138	0.2
KL32-04	345	348	1.02	10200	0.51	1.9	161	51	14	570	0.01	29	0.2	9.0	184	0.01
KL32-04	348	351	1.09	10900	0.6	1.4	324	34	7	365	1	20	0.01	16.5	153	0.01
KL32-04	351	354	1.41	14100	0.76	2	400	58	5	1000	1	17	0.2	15.5	197	0.01
KL32-04	354	357	0.83	8300	0.4	1.4	1920	237	20	417	0.01	15	0.2	10.0	123	0.38
KL32-04	357	360	0.86	8600	0.41	1.4	540	97	13	304	0.01	13	0.2	9.0	125	0.3
KL32-04	360	363	1.74	17400	0.53	2.4	187	45	18	302	0.01	19	0.4	16.0	137	0.12
KL32-04	363	366	1.85	18500	0.76	2.4	200	167	410	304	0.01	16	2.2	14.5	132	0.01
KL32-04	366	369	0.96	9600	0.42	1.4	360	160	210	423	0.01	11	1.5	10.0	117	0.1
KL32-04	369	372	1.39	13900	0.55	1.8	83	78	74	480	0.01	13	0.3	14.5	106	0.13
KL32-04	372	375	1.74	17400	0.46	2.7	90	34	580	575	0.01	20	2.6	14.0	135	0.22
KL32-04	375	378	2.01	20100	0.35	3.4	660	141	1350	1340	2	19	18	11.0	95	0.65
KL32-04	378	381	2.39	23900	0.75	4.1	1000	281	880	1540	2	27	24	9.0	73	1.3
KL32-04	381	384	2.76	27600	1.13	4	146	68	210	690	1	25	3.2	17.5	108	0.84
KL32-04	384	387	1.82	18200	0.64	3.1	610	178	27	334	1	24	0.4	10.0	116	0.54
KL32-04	387	390	0.85	8500	0.33	3.2	3700	650	1070	123	1	25	37	13.0	156	2.76
KL32-04	390	393	1.89	18900	0.71	3	460	130	130	390	0.01	24	0.3	10.0	80	0.27
KL32-04	393	396	2.54	25400	1.43	10.7	4800	11400	180	840	1	31	6	25.0	48	0.98
KL32-04	396	399	3.14	31400	1.27	4.4	600	10500	120	435	1	46	2.1	24.0	136	0.18
KL32-04	399	402	4.04	40400	1.35	4	130	38	61	334	1	70	0.5	21.0	160	0.01
KL32-04	402	405	1.99	19900	0.69	3.1	520	490	71	590	1	39	0.4	20.0	87	0.35
KL32-04	405	408	0.92	9200	0.8	2.7	430	343	260	470	1	33	16.7	11.8	93	0.28
KL32-04	408	411	0.303	3030	0.12	1	127	46	18	304	1	23	0.6	10.3	130	0.01
KL32-04	411	414	0.474	4740	0.19	2	900	399	420	620	3	76	20	19.0	155	0.22
KL32-04	414	417	0.33	3300	0.08	1	670	174	290	474	1	66	6.5	24.2	131	0.14
KL32-04	417	420	0.54	5400	0.14	2.6	270	233	1030	580	2	30	26	12.5	207	0.1
KL32-04	420	423	1.23	12300	0.15	2.3	175	195	590	660	1	31	6.9	20.0	314	0.01
KL32-04	423	426	1.73	17300	0.2	3.1	114	275	500	465	1	46	2.4	26.7	291	0.1
KL32-04	426	429	1.71	17100	0.32	6.1	254	256	270	357	1	39	3.2	17.9	354	0.2

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL32-04	429	432	2.88	28800	0.6	7	137	670	15	247	1	37	0.3	26.0	302	0.14
KL32-04	432	433.6	2.76	27600	0.92	6	550	137	12	540	1	47	0.4	30.0	278	0.01
KL32-04	433.6	435	5.95	59500	2	13.4	4400	10700	18	60	1	90	0.8	47.5	124	0.12
KL32-04	435	438	2.54	25400	1.55	9.5	500	3800	10	150	1	68	0.5	28.0	248	0.01
KL32-04	438	441	1.48	14800	0.93	5.6	450	325	12	180	3	96	0.4	20.0	173	0.01
KL32-04	441	443	1.98	19800	1.59	10.6	3700	6100	12	780	4	110	0.3	21.0	93	0.13
KL32-04	443	444	1.82	18200	1.08	6.3	620	241	4	45	3	48	0.5	13.2	128	0.01
KL32-04	444	447	2.19	21900	1.22	6.1	2800	990	9	140	2	47	1.1	13.0	156	0.01
KL32-04	447	450	2.39	23900	2.12	12	6100	5800	28	42	5	56	1.6	25.0	149	0.01
KL32-04	450	453.2	6.86	68600	3.31	22.8	3800	1260	6	12	2	48	0.3	30.0	127	0.01
KL32-04	453.2	456	2.28	22800	1.34	7.2	412	59	30	100	6	31	1.3	17.0	202	0.01
KL32-04	456	457.8	1.09	10900	0.69	3.4	195	67	25	8	15	34	1	45.3	178	0.01
KL32-04	457.8	459	1.02	10200	0.8	4.6	400	36	7	18	22	12	0.2	12.8	50	0.01
KL32-04	459	462	0.89	8900	0.48	2.7	176	75	4	260	5	44	0.3	26.5	64	0.01
KL32-04	462	465	0.955	9550	0.51	3.2	300	41	3	14	4	56	0.3	7.3	28	0.01
KL32-04	465	468	2.43	24300	1.56	11	530	98	5	8	3	49	0.5	11.0	26	0.01
KL32-04	468	469.15	1.12	11200	0.82	6.4	237	46	53	15	10	32	2	4.8	41	0.01
KL32-04	469.15	471	2.49	24900	1.31	23.5	570	87	37	15	4	31	2.4	12.0	36	0.01
KL32-04	471	474	1.67	16700	3.2	14.6	450	253	38	28	5	30	2.6	8.5	263	0.01
KL32-04	474	475.65	3.13	31300	1.47	36.7	870	268	14	110	26	97	1.3	46.0	213	0.01
KL32-04	475.65	480	2	20000	1.33	24.7	500	72	20	16	25	46	0.7	21.0	69	0.01
KL32-04	480	481.85	1.48	14800	1.4	24	3000	172	22	12	35	17	0.9	16.0	46	0.01
KL32-04	481.85	483	0.55	5500	0.81	7.6	391	46	60	5	16	14	1.6	8.8	99	0.01
KL32-04	483	486	0.509	5090	1.08	8.7	790	404	23	7	14	28	0.8	8.8	40	0.01
KL32-04	486	489	1.51	15100	1.6	14.4	2600	480	10	3	8	12	0.5	14.5	43	0.01
KL32-04	489	492	1.04	10400	0.48	3.7	104	26	11	4	3	14	0.4	21.3	100	0.01
KL32-04	492	495	0.429	4290	0.27	2.4	143	45	5	35	2	20	0.3	13.0	57	0.01
KL32-04	495	498	1.37	13700	1.19	8.7	160	29	8	7	0.01	31	0.4	16.5	50	0.01
KL32-04	498	501	0.38	3800	0.3	2.3	101	14	11	5	2	18	0.3	11.3	49	0.01
KL32-04	501	504	0.272	2720	0.19	2.1	151	38	13	10	2	20	0.3	7.5	75	0.01
KL32-04	504	506.4	0.89	8900	0.53	5.1	136	33	16	70	1	33	0.6	21.3	76	0.01
KL32-04	506.4	508.2	0.35	3500	0.21	1.7	105	18	9	58	1	14	0.4	19.0	27	0.01
KL32-04	508.2	510	0.57	5700	0.19	2.4	105	16	10	21	0.01	16	0.5	11.5	48	0.01
KL32-04	510	513	0.58	5800	0.19	2.4	80	53	7	103	0.01	12	0.4	14.8	92	0.01
KL32-04	513	516	0.81	8100	0.29	3.3	93	37	8	201	0.01	11	0.5	11.1	44	0.01
KL32-04	516	519	0.67	6700	0.13	2.1	59	18	2	24	0.01	10	0.01	6.8	50	0.01
KL32-04	519	522	0.59	5900	0.17	2.1	53	26	3	195	0.01	11	0.01	9.5	69	0.01
KL32-04	522	525	1.08	10800	0.11	2.5	47	20	7	70	0.01	8	0.3	13.5	58	0.01
KL32-04	525	527.1	0.442	4420	0.1	1.3	25	11	2	83	0.01	14	0.01	10.5	69	0.01
KL32-04	527.1	531	0.389	3890	0.12	1	34	12	2	28	0.01	16	0.01	7.8	44	0.01
KL32-04	531	534	0.234	2340	0.13	0.6	51	13	1	710	0.01	12	0.01	7.0	50	0.01
KL32-04	534	537	0.43	4300	0.22	1.4	88	14	3	61	1	35	0.3	9.5	45	0.01
KL32-04	537	540	0.507	5070	0.45	1.7	97	49	1	66	0.01	14	0.01	9.2	56	0.01
KL32-04	540	543	0.69	6900	0.07	1.6	80	43	2	95	0.01	18	0.2	14.0	136	0.01
KL32-04	543	546	1.05	10500	0.24	3.2	70	24	3	250	0.01	20	0.2	12.0	67	0.01
KL32-04	546	549	0.447	4470	0.13	1.3	145	42	3	85	0.01	23	0.2	15.3	142	0.01
KL32-04	549	550.95	0.63	6300	0.11	1.9	50	30	3	98	1	35	0.01	18.4	84	0.01
KL32-04	550.95	552	1.13	11300	0.08	3	51	17	1	1100	0.01	14	0.01	13.0	32	0.01
KL32-04	552	555	0.491	4910	0.13	2.4	540	820	2	113	0.01	17	2.3	16.8	87	0.01
KL32-04	555	558	0.289	2890	0.06	1.1	97	61	7	34	0.01	10	1.1	7.5	100	0.01
KL32-04	558	559.5	0.171	1710	0.04	1.7	54	30	1	14	0.01	4	0.3	3.5	84	0.01
KL32-04	559.5	561	0.378	3780	0.03	1.4	137	72	1	21	0.01	8	0.2	6.5	166	0.01
KL32-04	561	563.8	0.447	4470	0.07	1.5	100	42	3	185	0.01	18	0.4	7.8	95	0.01
KL32-04	563.8	566.8	0.234	2340	0.06	0.9	67	23	9	401	0.01	36	1.7	11.4	39	0.01
KL32-04	566.8	570	0.392	3920	0.06	1.5	297	194	65	88	0.01	21	5.4	14.2	69	0.01
KL32-04	570	573	0.304	3040	0.05	1.4	125	168	4	550	0.01	12	0.4	8.8	71	0.01
KL32-04	573	574.7	0.61	6100	0.22	2.4	32	19	1	155	0.01	12	0.4	10.3	47	0.01
KL32-04	574.7	576	1.26	12600	0.11	1.2	51	27	94	130	0.01	15	8.9	10.5	135	0.18
KL32-04	576	579	0.71	7100	0.04	0.8	26	13	90	143	1	18	4	10.5	169	0.18
KL32-04	579	582	0.59	5900	0.07	4.1	38	16	58	158	1	21	2.2	8.8	155	0.16
KL32-04	582	585	0.72	7200	0.11	1.4	32	11	29	380	1	24	1.8	10.9	153	0.1
KL32-04	585	588.85	0.62	6200	0.3	2.1	53	32	400	480	1	23	24	8.8	150	0.34
KL32-04	588.85	591	0.402	4020	0.23	1.6	49	26	7	121	0.01	12	0.4	4.3	109	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL32-04	591	594	0.385	3850	0.16	1.1	39	23	2	83	0.01	7	0.4	5.2	96	0.01	
KL32-04	594	597	0.331	3310	0.13	1	21	18	1	205	0.01	7	0.01	4.8	62	0.01	
KL32-04	597	600	0.344	3440	0.12	1	37	8	0.01	113	0.01	6	0.01	4.3	43	0.01	
KL32-04	600	603	0.259	2590	0.11	1	48	5	0.01	103	0.01	6	0.01	4.0	30	0.01	
KL32-04	603	606	0.118	1180	0.05	0.01	25	7	0.01	93	0.01	0.01	1.8	2.0	28	0.01	
KL32-04	606	609	0.177	1770	0.07	1	57	44	22	190	1	4	1.4	5.0	27	0.01	
KL32-04	609	612	0.99	9900	0.34	2.4	104	69	16	375	0.01	17	0.7	8.7	202	0.01	
KL32-04	612	615	0.32	3200	0.16	5.6	9800	8900	29	70	1	10	5.7	8.0	104	0.15	
KL32-04	615	618	0.445	4450	0.2	1.6	175	118	140	188	1	28	0.9	15.7	155	0.01	
KL32-04	618	621	0.88	8800	0.34	2.5	68	68	25	450	1	37	1.1	18.0	205	0.01	
KL32-04	621	624.65	0.429	4290	0.16	1.5	35	21	2	195	0.01	17	0.2	14.0	114	0.01	
KL32-04	624.65	627.6	0.64	6400	0.23	2	45	16	1	1650	0.01	24	0.01	10.0	91	0.01	
KL32-04	627.6	630	0.8	8000	0.4	2.3	88	10	0.01	427	0.01	28	0.01	12.3	70	0.01	
KL32-04	630	633.2	1.08	10800	0.43	3.1	120	34	4	440	0.01	49	0.01	14.8	75	0.01	
KL32-04	633.2	636	0.77	7700	0.4	2.1	96	12	2	175	0.01	22	0.01	7.3	57	0.01	
KL32-04	636	639	3.89	38900	1.37	10.1	327	16	0.01	63	0.01	50	0.01	21.0	55	0.01	
KL32-04	639	641.9	1.05	10500	0.38	2.7	120	9	4	30	0.01	25	0.01	7.5	47	0.01	
KL32-04	641.9	645	2.2	22000	0.72	6.3	178	13	3	520	0.01	33	0.01	8.5	31	0.01	
KL32-04	645	648	2.47	24700	1.02	6.3	285	34	3	4050	0.01	30	0.01	14.0	27	0.01	
KL32-04	648	650.4	2.19	21900	0.55	5.5	130	14	2	614	0.01	24	0.01	8.0	15	0.01	
KL32-04	650.4	654	2.6	26000	1.24	7	190	15	4	1350	0.01	36	0.2	19.0	85	0.01	
KL32-04	654	657	1.43	14300	0.64	3.7	117	12	8	80	0.01	26	0.01	11.0	35	0.01	
KL32-04	657	660	0.75	7500	0.41	2.1	70	15	7	68	0.01	26	0.01	9.3	27	0.01	
KL32-04	660	663	1.16	11600	0.65	3.4	104	9	5	55	0.01	18	0.01	9.3	57	0.01	
KL32-04	663	666	1.59	15900	1.21	4.5	155	18	2	43	0.01	29	0.01	12.5	42	0.01	
KL32-04	666	669	1.07	10700	0.55	2.4	81	9	7	40	0.01	27	0.01	9.5	27	0.01	
KL32-04	669	672	0.82	8200	0.4	1.9	114	53	4	28	0.01	27	1	9.0	24	0.01	
KL32-04	672	675	1.16	11600	0.6	3.4	95	11	3	25	0.01	24	0.01	9.0	30	0.01	
KL32-04	675	678	1.01	10100	0.36	2.5	105	11	2	25	0.01	25	0.01	8.0	31	0.01	
KL32-04	678	681	0.57	5700	0.23	1.5	124	17	2	30	0.01	23	0.01	7.0	17	0.01	
KL32-04	681	684	1.62	16200	0.63	3.7	127	8	3	23	0.01	30	0.01	14.0	16	0.01	
KL32-04	684	687	0.83	8300	0.3	1.5	100	12	3	115	0.01	26	0.2	10.1	45	0.01	
KL32-04	687	690	1.35	13500	0.52	2.6	112	7	3	40	0.01	26	0.01	15.0	36	0.01	
KL32-04	690	693	0.9	9000	0.46	1.7	145	8	1	14	0.01	19	0.01	8.1	26	0.01	
KL32-05	0	3	0.0186	186	0.01	0.01	119	55	22	2	0.01	2	0.01	1.5	0.8	113	0.01
KL32-05	3	6	0.0055	55	0.03	0.01	269	92	11	0.01	0.01	0.01	1.1	0.8	43	0.01	
KL32-05	6	9	0.0029	29	0.03	0.01	151	47	14	4	0.01	0.01	1.3	1.3	74	0.01	
KL32-05	9	12	0.0025	25	0.01	0.01	125	38	15	3	0.01	0.01	0.8	1.3	70	0.01	
KL32-05	12	15	0.0097	97	0.01	0.01	114	34	13	2	0.01	3	0.5	1.8	29	0.01	
KL32-05	15	18	0.007	70	0.02	0.6	246	94	20	3	0.01	0.01	0.8	4.0	27	0.01	
KL32-05	18	21	0.0084	84	0.01	1.2	207	98	27	2	2	0.01	1.1	2.3	30	0.01	
KL32-05	21	24	0.0061	61	0.01	1	189	580	17	3	0.01	0.01	0.8	1.0	27	0.01	
KL32-05	24	27	0.0095	95	0.02	4.5	1070	1970	37	18	11	0.01	2.5	6.3	26	0.01	
KL32-05	27	30	0.0095	95	0.02	4.5	1070	1970	37	18	11	0.01	2.5	6.3	26	0.01	
KL32-05	30	33	0.005	50	0.09	3.6	590	1400	110	7	6	0.01	4.1	3.2	25	0.1	
KL32-05	33	36	0.0113	113	0.37	4.6	1490	1750	80	4	2	0.01	10.7	5.3	21	0.13	
KL32-05	36	39	0.0027	27	0.02	0.8	234	640	26	4	1	0.01	2.4	1.3	23	0.01	
KL32-05	39	42	0.0027	27	0.24	1	292	540	77	3	0.01	0.01	3.1	1.8	24	0.1	
KL32-05	42	45	0.003	30	0.07	0.7	174	870	60	0.01	0.01	0.01	1.5	2.5	34	0.01	
KL32-05	45	48	0.0018	18	0.03	0.01	81	183	22	0.01	0.01	0.01	0.5	1.5	28	0.01	
KL32-05	48	51	0.002	20	0.01	0.5	136	560	9	2	0.01	0.01	0.4	1.8	27	0.01	
KL32-05	51	54	0.0047	47	0.01	0.01	50	128	13	2	0.01	0.01	1.3	1.8	32	0.01	
KL32-05	54	57	0.0042	42	0.01	1.1	235	360	40	12	2	0.01	1.4	3.0	56	0.01	
KL32-05	57	60	0.0023	23	0.02	0.6	193	142	76	13	0.01	3	2.9	0.5	65	0.01	
KL32-05	60	61.5	0.0187	187	0.02	0.7	104	134	38	5	1	2	3.2	0.0	133	0.01	
KL32-05	61.5	63	0.161	1610	0.04	3.5	108	214	40	13	4	13	1.7	19.5	120	0.01	
KL32-05	63	64.5	0.0104	104	0.07	0.9	145	167	53	6	2	4	1.5	1.3	99	0.01	
KL32-05	64.5	66	0.018	180	0.04	2.6	2240	364	50	6	4	0.01	2.8	5.3	13	0.23	
KL32-05	66	68.6	0.0112	112	0.04	3.7	800	1410	38	13	2	0.01	4.6	5.1	21	0.01	
KL32-05	68.6	72	0.054	540	0.38	6.4	330	490	130	32	19	12	4.5	2.8	89	0.17	
KL32-05	72	75	0.056	560	0.12	8.6	248	760	130	4	36	3	6.6	12.4	83	0.1	
KL32-05	75	78	0.0099	99	0.05	1.4	87	85	56	6	7	0.01	5.9	2.7	126	0.01	
KL32-05	78	81	0.67	6700	0.28	6.8	195	490	530	10	32	2	30	14.2	218	0.11	

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL32-05	81	82	0.0104		104	0.04	2.4	2330	940	18	12	18	0.01	1	1.8	24	0.01
KL32-05	82	84	0.0315		315	0.28	1.9	152	184	160	3	23	0.01	5.6	2.3	23	0.1
KL32-05	84	87	1.02		10200	0.28	39	2700	1160	1540	4	660	5	66	26.3	80	0.3
KL32-05	87	88	4.82		48200	0.32	73	540	1770	660	37	1200	6	26	25.0	64	0.32
KL32-05	88	90	0.25		2500	0.2	15.1	281	790	530	21	63	4	19.9	9.6	190	0.01
KL32-05	90	93	0.141		1410	0.35	20.6	334	2700	540	14	92	4	21	7.5	234	0.12
KL32-05	93	96	0.0302		302	0.35	4.8	164	970	180	2	28	5	16.7	6.3	28	0.1
KL32-05	96	99	0.0359		359	0.17	3.6	860	580	140	24	28	0.01	11.7	3.5	23	0.01
KL32-05	99	101.8	0.0132		132	0.18	3.3	283	590	65	8	14	0.01	2.7	2.0	30	0.01
KL32-05	101.8	104.1	0.0185		185	0.11	3	890	700	120	6	15	0.01	4.9	2.0	29	0.01
KL32-05	104.1	107	0.06		600	0.05	11.6	9000	7400	150	7	43	3	16.8	14.5	26	0.1
KL32-05	107	110	0.0036		36	0.06	2.8	730	1420	13	14	3	0.01	1.6	1.8	20	0.01
KL32-05	110	113	0.0042		42	0.03	2	960	1290	9	10	1	0.01	1.8	1.3	21	0.01
KL32-05	113	116	0.0033		33	0.04	3.4	560	690	20	4	6	0.01	1.3	4.8	23	0.01
KL32-05	116	119	0.0148		148	0.04	3.2	840	920	45	0.01	4	0.01	2.5	3.8	24	0.01
KL32-05	119	122	0.0078		78	0.06	4.7	1480	1610	23	7	7	0.01	1.8	3.3	23	0.01
KL32-05	122	125	0.0118		118	0.05	12.7	1670	1490	36	2	30	0.01	3.3	4.3	23	0.01
KL32-05	125	128	0.0031		31	0.05	2.1	94	196	17	4	5	0.01	0.4	4.5	27	0.01
KL32-05	128	131	0.0087		87	0.03	4.6	296	360	34	0.01	16	0.01	1.5	4.0	29	0.01
KL32-05	131	134	0.0056		56	0.02	2.4	700	347	12	0.01	6	0.01	1	1.8	31	0.01
KL32-05	134	137	0.0027		27	0.05	4	104	205	6	0.01	12	0.01	0.4	1.8	25	0.01
KL32-05	137	140	0.0049		49	0.04	4.3	116	286	15	4	14	0.01	0.7	3.5	30	0.01
KL32-05	140	143	0.0041		41	0.03	2.1	184	282	16	4	6	0.01	0.6	2.5	32	0.01
KL32-05	143	146	0.0065		65	0.03	3.1	440	640	24	0.01	6	0.01	1	1.8	33	0.01
KL32-05	146	149	0.0035		35	0.02	4.6	289	590	12	3	15	0.01	0.8	1.5	32	0.01
KL32-05	149	152	0.0027		27	0.04	1.6	123	409	12	4	3	0.01	0.7	1.0	27	0.01
KL32-05	152	155	0.0705		705	0.04	6.6	2420	4720	65	10	13	0.01	10.3	4.3	19	0.01
KL32-05	155	158	0.0339		339	0.08	16.6	15100	14100	18	38	30	0.01	4.7	12.5	18	0.01
KL32-05	158	161	0.0075		75	0.06	3	4150	3490	18	15	0.01	0.01	2.8	2.3	60	0.01
KL32-05	161	164	0.0408		408	0.1	16.3	27900	8400	65	12	28	0.01	9.1	13.3	18	0.17
KL32-05	164	168	0.0112		112	0.02	3.6	420	630	31	0.01	5	0.01	2	2.0	17	0.01
KL32-05	168	170	0.0061		61	0.01	3.7	2110	2900	12	5	3	0.01	3.5	1.8	18	0.01
KL32-05	170	173	0.0182		182	0.02	7	3800	7700	19	5	1	0.01	9.1	4.8	17	0.01
KL32-05	173	176	0.0033		33	0.01	1.3	940	1330	4	5	1	0.01	1	1.0	12	0.01
KL32-05	176	179	0.0029		29	0.03	1.8	1780	810	10	11	3	0.01	5.7	2.0	15	0.01
KL32-05	179	182	0.012		120	0.07	4.9	6700	3700	32	14	6	0.01	2.9	5.9	16	0.01
KL32-05	182	185	0.086		860	0.2	21	18500	4300	220	48	26	5	19.3	13.8	21	0.16
KL32-05	185	188	0.0349		349	0.11	1.8	364	550	18	15	1	0.01	0.8	4.3	20	0.01
KL32-05	188	191	0.0273		273	0.08	1.2	540	366	17	10	1	0.01	0.7	3.5	16	0.01
KL32-05	191	192.85	0.169		1690	0.19	3.9	9700	1160	16	10	7	10	1.2	9.3	17	0.01
KL32-05	192.85	194	0.0205		205	0.03	0.01	540	331	7	14	0.01	0.01	0.6	1.8	16	0.01
KL32-05	194	197	0.0133		133	0.03	1.1	500	238	14	13	2	0.01	1.2	3.3	15	0.01
KL32-05	197	200	0.031		310	0.05	0.9	450	247	12	7	2	0.01	0.8	2.5	17	0.01
KL32-05	200	203	0.064		640	0.03	0.7	285	305	12	10	1	0.01	1.6	1.8	22	0.01
KL32-05	203	206	0.021		210	0.03	0.7	480	351	17	9	3	0.01	3.1	2.3	20	0.01
KL32-05	206	209	0.055		550	0.04	6.7	1550	4210	21	4	2	0.01	13.3	4.8	18	0.01
KL32-05	209	212	0.0215		215	0.02	3.7	2850	3520	8	12	1	0.01	4.6	4.8	24	0.01
KL32-05	212	215	0.0197		197	0.07	2	940	970	27	14	4	0.01	3.6	6.3	23	0.01
KL32-05	215	218	0.0213		213	0.43	2.1	1240	1270	66	14	4	0.01	18.9	3.5	26	0.01
KL32-05	218	220.1	0.0273		273	0.17	5	1910	3300	65	18	30	0.01	5	15.8	32	0.01
KL32-05	220.1	222.1	0.0116		116	0.06	2.5	780	1180	15	13	7	0.01	0.8	6.8	21	0.01
KL32-05	222.1	225	0.0181		181	0.1	2.4	2010	1770	38	19	4	0.01	2.2	8.5	18	0.01
KL32-05	225	228	0.077		770	0.13	3	1850	2660	21	22	7	0.01	7.8	12.0	16	0.01
KL32-05	228	231	0.072		720	0.15	18.8	8400	8300	39	19	83	0.01	2.7	40.0	21	0.01
KL32-05	231	234.75	0.171		1710	0.51	8.1	8200	2500	68	303	28	4	2.8	19.5	15	0.01
KL32-05	234.75	236.1	0.87		8700	1.28	27.4	4100	880	40	45	95	25	2	45.0	25	0.01
KL32-05	236.1	239.9	0.168		1680	0.35	4.4	2760	385	39	143	26	5	2.4	15.3	29	0.01
KL32-05	239.9	241.4	1.4		14000	2.63	30	6200	150	93	10	59	50	1.3	39.0	30	0.01
KL32-05	241.4	245	0.51		5100	1.32	13	7100	600	84	120	50	20	4.6	19.3	24	0.63
KL32-05	245	248	0.198		1980	0.37	3.7	653	277	78	2070	42	8	10.7	6.8	60	0.01
KL32-05	248	251	0.3		3000	1.29	8.8	4800	1170	360	1460	44	9	34	12.0	60	0.68
KL32-05	251	254	0.23		2300	1.05	7.9	5300	2900	140	635	19	9	20.4	12.0	35	0.52
KL32-05	254	257	0.63		6300	1.01	14.2	22100	620	240	720	480	110	7	31.5	30	0.22

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL32-05	257	260	0.48	4800	1.09	19.2	6000	2800	200	920	176	21	24	13.0	27	0.29
KL32-05	260	263	1.06	10600	1.81	24.7	21000	400	67	1200	250	90	1.9	45.8	21	0.01
KL32-05	263	266	1.1	11000	1.04	17.8	2700	1140	66	452	24	38	3.7	14.5	16	0.01
KL32-05	266	269	1.15	11500	0.73	18.2	2200	580	100	600	75	35	1.5	16.0	14	0.01
KL32-05	269	272	0.51	5100	0.45	14.2	19800	326	84	60	187	29	1.3	15.5	29	0.01
KL32-05	272	275	0.87	8700	0.61	16.9	16500	271	96	70	54	52	1	12.3	12	0.01
KL32-05	275	278	0.98	9800	1.56	21.8	8200	381	110	150	105	117	3	22.8	25	0.01
KL32-05	278	279.5	1.37	13700	1.77	20	730	222	68	298	83	31	4	18.5	33	0.01
KL32-05	279.5	281	0.373	3730	0.4	4.1	327	137	36	200	20	15	5.1	12.8	15	0.01
KL32-05	281	284	0.177	1770	0.22	1.8	320	197	100	119	13	19	6.2	22.3	54	0.01
KL32-05	284	287	0.58	5800	0.85	3.5	301	223	70	87	14	13	4.7	13.3	35	0.01
KL32-05	287	288.5	0.83	8300	1.23	8.2	352	170	150	190	18	16	5.2	15.5	43	0.01
KL32-05	288.5	290	1.01	10100	1.17	9.8	940	200	140	4960	30	36	6.7	14.7	175	0.01
KL32-05	290	293	0.87	8700	2.02	13.2	2400	401	140	175	192	42	3.7	39.5	115	0.01
KL32-05	293	296	2.25	22500	2.06	16.2	600	140	63	83	40	43	3.3	43.0	49	0.01
KL32-05	296	299	2.12	21200	1.62	9	364	125	22	115	26	51	2.3	35.0	121	0.01
KL32-05	299	300.7	2.42	24200	1.5	6.8	346	98	25	55	3	33	1.7	32.0	35	0.01
KL32-05	300.7	302	5.06	50600	3.16	9.9	570	75	2	34	1	46	0.8	22.5	37	0.01
KL32-05	302	305	3.4	34000	2.4	9.6	830	70	5	25	3	51	0.8	27.5	25	0.01
KL32-05	305	308	3.13	31300	2.53	9.6	1450	590	7	16	5	42	1.1	17.0	47	0.01
KL32-05	308	311	4.84	48400	4.85	10	2200	131	17	32	4	91	1.4	20.0	24	0.01
KL32-05	311	314	2.48	24800	2.5	12.5	372	70	12	2	2	44	1.3	9.0	26	0.01
KL32-05	314	316.5	3.1	31000	1.55	10.3	800	231	240	70	1	45	5.3	18.0	59	0.25
KL32-05	316.5	319.25	1.44	14400	0.13	3.5	197	75	540	146	0.01	19	5	13.2	166	1.24
KL32-05	319.25	322.1	3.02	30200	0.48	6.5	162	52	250	193	0.01	30	3	20.0	82	0.25
KL32-05	322.1	325	1.8	18000	0.21	3.1	118	58	180	346	0.01	25	1.6	17.5	117	0.14
KL32-05	325	328	0.95	9500	0.11	2.3	108	31	270	323	0.01	29	22	13.8	37	0.27
KL32-05	328	331	0.74	7400	0.13	2	96	47	130	480	0.01	12	6.1	10.8	147	0.1
KL32-05	331	333	1.51	15100	0.16	5.5	275	107	320	392	0.01	16	6.2	10.5	88	0.19
KL32-05	333	337.5	1	10000	0.17	7.1	1920	860	280	284	0.01	15	9.6	9.5	76	0.36
KL32-05	337.5	340	1.47	14700	0.26	4.7	183	70	110	170	0.01	31	6.3	12.0	69	0.01
KL32-05	340	343	1.67	16700	0.32	4	163	59	85	240	0.01	32	32	7.5	75	0.01
KL32-05	343	346	1.65	16500	0.39	6.5	1800	750	360	357	0.01	33	204	8.8	59	0.3
KL32-05	346	349	1.66	16600	0.34	3.7	89	66	33	540	0.01	37	5.3	8.5	92	0.01
KL32-05	349	352	1.97	19700	1.16	3.2	77	49	12	730	0.01	31	2	9.5	55	0.01
KL32-05	352	355	1.91	19100	0.25	6	850	660	2100	1100	2	23	140	10.5	39	0.31
KL32-05	355	358	2.09	20900	0.35	3	660	186	140	1440	0.01	17	46	4.5	229	0.01
KL32-05	358	361	2.29	22900	0.47	9	4000	890	110	480	0.01	19	96	7.5	40	0.1
KL32-05	361	364	1.58	15800	0.23	5.2	530	166	91	580	0.01	18	75	7.0	195	0.01
KL32-05	364	367	2.3	23000	0.29	9.1	4500	1200	100	1100	0.01	20	100	12.5	236	0.2
KL32-05	367	370	0.93	9300	0.46	5.3	5900	4300	87	580	0.01	16	50	8.1	246	0.15
KL32-05	370	372.6	1.37	13700	0.41	3.3	149	90	14	362	1	19	3	5.0	152	0.01
KL32-05	372.6	376	1.42	14200	0.26	4.5	116	70	41	570	0.01	20	60	4.5	59	0.01
KL32-05	376	379	1.43	14300	0.16	2.2	210	80	220	560	0.01	14	60	10.5	110	0.01
KL32-05	379	382	1.48	14800	0.37	6	840	261	38	620	0.01	19	6.3	9.5	140	0.01
KL32-05	382	385	1.29	12900	0.6	2.1	116	49	6	309	0.01	14	2.4	9.0	106	0.01
KL32-05	385	388	0.99	9900	0.39	3.1	212	168	21	189	0.01	13	3.3	5.5	55	0.01
KL32-05	388	391	1.86	18600	0.81	2.7	164	128	7	86	1	14	2.2	5.0	118	0.01
KL32-05	391	394	4.01	40100	2.14	4.9	135	203	7	17	1	24	0.8	12.5	65	0.01
KL32-05	394	394.65	1.76	17600	1.3	12.8	2000	1440	120	95	70	21	10	11.5	119	0.2
KL32-05	394.65	397.5	2.79	27900	1.38	4.1	208	247	2	16	1	20	0.9	11.6	87	0.01
KL32-05	397.5	400.35	1.99	19900	0.93	2.6	131	105	13	183	1	15	0.9	7.5	134	0.01
KL32-05	400.35	402.6	2.62	26200	0.68	4.6	68	147	87	353	1	10	3	12.0	203	0.22
KL32-05	402.6	405	0.456	4560	0.16	4.8	337	980	49	272	5	4	2.9	5.1	215	0.01
KL32-05	405	408	1	10000	0.5	18.7	680	380	160	490	30	5	13.8	5.8	237	0.33
KL32-05	408	411	0.86	8600	0.37	13.1	378	327	96	630	17	3	45	4.0	296	0.3
KL32-05	411	414	0.82	8200	0.21	4.1	620	345	85	530	3	7	26	5.5	165	0.21
KL32-05	414	417	0.66	6600	0.13	1.5	148	107	200	450	1	7	2.8	6.0	168	0.01
KL32-05	417	420	0.79	7900	0.16	1.3	154	101	120	251	0.01	6	7.2	3.8	258	0.01
KL32-05	420	423	0.465	4650	0.11	1.5	198	135	620	740	0.01	2	3.2	5.8	280	0.01
KL32-05	423	426	0.496	4960	0.14	5.3	1890	3500	580	640	5	2	3.4	5.3	270	0.26
KL32-05	426	429	0.505	5050	0.21	2.3	396	231	670	297	1	3	2.7	3.5	271	0.01
KL32-05	429	432	0.521	5210	0.14	2	280	149	670	1350	1	4	2.2	5.3	120	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL32-05	432	435	0.501	5010	0.17	9.6	540	620	1660	3960	1	3	50	6.3	217	0.3
KL32-05	435	438	0.66	6600	0.17	1.8	740	210	530	1180	1	4	0.8	6.5	132	0.01
KL32-05	438	441	0.71	7100	0.25	0.7	36	18	55	425	1	3	0.2	5.8	136	0.01
KL32-05	441	444	1.13	11300	0.51	13.5	400	281	400	770	6	3	80	7.8	128	0.45
KL32-05	444	447	1.22	12200	0.28	2	120	56	180	351	1	3	0.8	8.0	176	0.01
KL32-05	447	450	0.74	7400	0.17	1.3	81	32	280	510	0.01	3	1.7	6.0	179	0.01
KL32-05	450	453	0.62	6200	0.13	0.9	82	43	7	393	0.01	4	6	5.3	165	0.1
KL32-05	453	456	1.59	15900	0.56	25.7	182	94	230	463	17	20	40	6.5	151	0.21
KL32-05	456	459	1.02	10200	0.57	53	860	287	520	149	41	10	78	4.8	156	0.53
KL32-05	459	462	0.453	4530	0.21	7	3700	3540	22	82	2	10	2	4.8	162	0.01
KL32-05	462	465	0.78	7800	0.29	2.2	137	56	5	40	0.01	12	0.3	5.5	153	0.01
KL32-05	465	468	0.83	8300	0.33	1.7	125	52	7	50	0.01	9	0.5	6.7	570	0.01
KL32-05	468	471	0.534	5340	0.16	8.5	800	680	79	276	9	5	30	6.3	406	0.11
KL32-05	471	474	0.321	3210	0.09	10.7	276	265	81	113	7	5	34	4.8	560	0.01
KL32-05	474	477	0.435	4350	0.07	1.8	218	63	130	47	0.01	5	52	4.0	154	0.01
KL32-05	477	480	0.384	3840	0.08	1.4	208	90	52	164	0.01	4	34	5.3	362	0.01
KL32-05	480	483	0.71	7100	0.19	1.1	49	15	2	160	0.01	14	0.2	8.1	289	0.01
KL32-05	483	486	0.73	7300	0.17	0.9	48	10	3	66	0.01	11	0.7	6.0	190	0.01
KL32-05	486	489	0.57	5700	0.13	0.9	41	15	2	192	0.01	9	0.01	4.3	184	0.01
KL32-05	489	492	0.464	4640	0.14	0.7	55	21	3	60	0.01	8	0.3	4.6	362	0.01
KL32-05	492	495	0.507	5070	0.11	0.9	71	21	17	104	0.01	8	1.6	4.8	354	0.01
KL32-05	495	498	0.463	4630	0.07	1.3	264	182	110	172	1	7	28	5.6	412	0.01
KL32-05	498	501	0.454	4540	0.06	1.2	720	450	40	60	0.01	8	7	6.5	392	0.01
KL32-05	501	504	0.521	5210	0.04	0.6	62	14	11	124	0.01	6	0.4	5.0	181	0.01
KL32-05	504	507	0.401	4010	0.05	0.6	76	22	11	760	0.01	5	2.6	4.0	148	0.01
KL32-05	507	510	0.311	3110	0.03	0.8	590	287	30	114	0.01	7	2.4	4.0	343	0.01
KL32-05	510	513	0.331	3310	0.03	1	137	30	23	93	0.01	6	3	3.5	400	0.01
KL32-05	513	516	0.408	4080	0.04	0.5	31	13	10	103	0.01	6	0.5	4.3	412	0.01
KL32-05	516	519	0.55	5500	0.08	0.9	37	12	3	249	0.01	7	0.4	4.0	404	0.01
KL32-05	519	522	0.492	4920	0.04	0.8	35	12	6	170	0.01	9	0.8	5.6	545	0.01
KL32-05	522	525	0.459	4590	0.14	0.9	34	12	4	63	0.01	15	1.6	5.0	470	0.01
KL32-05	525	528	0.76	7600	0.1	1.3	97	31	18	168	0.01	13	3	5.8	335	0.01
KL32-05	528	531	0.381	3810	0.03	0.5	21	10	3	79	0.01	11	1	4.2	149	0.01
KL32-05	531	534	0.319	3190	0.03	0.7	74	21	97	86	1	10	7.2	3.6	142	0.01
KL32-05	534	536.2	0.292	2920	0.04	4.2	530	610	120	200	14	9	12	5.1	382	0.01
KL32-05	536.2	540	0.519	5190	0.17	1.3	55	14	4	93	0.01	17	0.6	6.3	262	0.01
KL32-05	540	543	0.525	5250	0.19	1.3	127	11	0.01	16	1	33	0.01	11.8	35	0.01
KL32-05	543	546	0.476	4760	0.24	1.2	106	5	0.01	22	0.01	31	0.01	6.6	24	0.01
KL32-05	546	549	1.23	12300	0.54	3.8	150	6	0.01	50	0.01	36	0.01	11.0	33	0.01
KL32-05	549	552	0.397	3970	0.18	1.1	97	6	0.01	21	0.01	33	0.01	7.2	14	0.01
KL32-05	552	555	0.62	6200	0.24	1	127	5	0.01	13	0.01	37	0.01	5.7	23	0.01
KL32-05	555	558	0.212	2120	0.08	0.5	86	5	0.01	11	0.01	30	0.01	3.2	16	0.01
KL32-05	558	561	0.64	6400	0.32	1.1	150	6	0.01	20	0.01	39	0.01	6.0	14	0.01
KL32-05	561	564	0.68	6800	0.44	1.5	168	7	0.01	132	0.01	38	0.3	5.8	16	0.01
KL32-05	564	565.5	0.97	9700	0.62	2	200	12	0.01	13	0.01	49	1.9	4.6	23	0.01
KL32-05	565.5	567	0.502	5020	0.32	1.1	71	8	5	11	0.01	20	0.01	7.0	16	0.01
KL32-05	567	570	0.22	2200	0.15	0.6	70	7	0.01	88	0.01	19	0.01	5.0	17	0.01
KL32-05	570	573	0.23	2300	0.15	0.5	82	5	0.01	11	0.01	29	0.01	0.7	24	0.01
KL32-05	573	576	1.85	18500	0.61	3.9	146	21	1	240	0.01	49	0.01	30.0	22	0.01
KL32-05	576	579	1.33	13300	0.33	2.1	63	6	1	690	0.01	28	0.01	15.5	32	0.01
KL32-05	579	582	0.51	5100	0.2	2	120	23	22	63	0.01	27	0.3	7.9	41	0.01
KL32-05	582	585	0.18	1800	0.06	0.5	63	6	13	28	0.01	21	0.01	2.2	26	0.01
KL32-05	585	588	0.497	4970	0.14	1.2	60	5	5	160	0.01	23	0.01	9.3	24	0.01
KL32-05	588	591	0.451	4510	0.17	1.2	79	8	0.01	50	0.01	28	0.01	11.2	38	0.01
KL32-05	591	594	0.382	3820	0.1	1	67	0.01	0.01	25	0.01	17	0.01	3.2	24	0.01
KL32-05	594	597	0.207	2070	0.04	0.01	34	0.01	0.01	7	0.01	14	0.01	3.8	42	0.01
KL32-05	597	600.2	0.398	3980	0.12	1	40	6	0.01	23	0.01	19	0.6	8.7	32	0.01
KL32-05	600.2	603	0.078	780	0.03	0.01	101	0.01	0.01	6	0.01	29	0.01	1.1	35	0.01
KL32-05	603	606	0.088	880	0.03	0.01	76	0.01	0.01	8	0.01	22	0.01	1.2	44	0.01
KL32-05	606	609	0.0385	385	0.04	0.01	114	0.01	0.01	2	0.01	30	0.01	1.5	31	0.01
KL32-05	609	612	0.422	4220	0.35	1	94	7	0.01	6	0.01	24	0.01	5.6	48	0.01
KL32-05	612	614.85	0.379	3790	0.35	0.7	81	5	0.01	11	0.01	17	0.01	4.5	44	0.01
KL32-05	614.85	618.6	0.185	1850	0.2	0.01	50	0.01	0.01	0.01	0.01	13	0.01	2.7	43	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL32-05	618.6	621.65	1.51	15100	0.51	2.8	104	0.01	0.01	11	0.01	24	0.01	13.0	40	0.01
KL32-05	621.65	624	0.301	3010	0.25	0.7	53	0.01	0.01	2	0.01	18	0.01	3.9	44	0.01
KL32-05	624	628.05	0.68	6800	0.21	1.7	93	0.01	0.01	6	0.01	26	0.01	8.5	32	0.01
KL32-05	628.05	630	0.64	6400	0.55	1.5	58	19	13	82	0.01	25	0.7	8.4	77	0.01
KL32-05	630	633	0.105	1050	0.04	0.01	33	6	0.01	12	0.01	13	0.2	2.6	28	0.01
KL32-05	633	636	0.184	1840	0.08	0.8	40	15	0.01	27	0.01	11	0.01	3.6	47	0.01
KL32-05	636	639	0.28	2800	0.08	1	41	5	0.01	8	0.01	11	0.01	2.7	60	0.01
KL32-05	639	642	0.094	940	0.04	0.7	800	560	2	15	1	10	0.01	1.7	61	0.01
KL32-05	642	645.45	0.104	1040	0.02	0.01	28	16	0.01	38	0.01	8	0.6	1.9	107	0.01
KL32-05	645.45	648	0.099	990	0.01	0.01	23	12	0.01	29	0.01	5	1.2	1.5	117	0.01
KL32-05	648	651	0.146	1460	0.01	0.01	30	12	0.01	109	0.01	7	0.2	2.3	110	0.01
KL32-05	651	654	0.166	1660	0.01	0.01	15	5	0.01	84	0.01	8	0.2	2.2	164	0.01
KL32-05	654	657	0.161	1610	0.01	0.01	24	11	0.01	58	0.01	9	0.2	2.5	162	0.01
KL32-05	657	658	0.205	2050	0.05	0.8	40	51	8	55	1	13	0.2	2.5	123	0.01
KL32-05	658	661	1.21	12100	0.4	1.7	70	12	0.01	17	0.01	32	0.2	16.0	31	0.01
KL32-05	661	663	0.169	1690	0.1	0.6	29	6	6	15	0.01	6	0.01	2.7	12	0.01
KL32-05	663	666	0.105	1050	0.02	0.01	73	39	7	12	0.01	5	0.01	1.6	44	0.01
KL32-05	666	669.2	0.159	1590	0.03	0.6	22	15	5	22	0.01	15	0.2	3.5	101	0.01
KL32-05	669.2	672	0.266	2660	0.04	2.4	162	110	450	118	0.01	13	8.8	4.7	104	1.19
KL32-05	672	675	0.265	2650	0.04	0.5	27	18	64	33	0.01	12	0.4	3.9	67	0.01
KL32-05	675	678	0.6	6000	0.1	1.6	24	5	21	233	0.01	24	0.3	7.8	78	0.01
KL32-05	678	681	0.61	6100	0.15	1.3	26	9	71	45	0.01	26	0.2	6.8	98	0.01
KL32-05	681	684	0.412	4120	0.07	0.8	24	29	3	41	0.01	22	0.2	6.0	95	0.01
KL32-05	684	689.5	0.381	3810	0.06	0.6	49	17	41	48	0.01	23	0.4	9.9	117	0.01
KL32-05	689.5	691.2	0.138	1380	0.02	0.8	111	312	140	42	0.01	13	1.1	3.3	78	0.01
KL32-05	691.2	694	0.136	1360	0.08	2.1	77	215	300	54	0.01	12	5.8	4.1	119	0.13
KL32-05	694	697	0.162	1620	0.04	2.3	144	245	330	88	1	19	6	6.0	100	0.26
KL32-05	697	699	0.076	760	0.01	3.3	2060	3970	66	61	0.01	10	4.5	3.6	115	0.33
KL32-05	699	702	0.073	730	0.01	3.5	346	3200	200	57	1	13	7.2	5.3	150	0.13
KL32-05	702	705	0.109	1090	0.01	1.6	50	92	120	67	0.01	14	2.8	4.2	144	0.01
KL32-05	705	708	0.168	1680	0.27	8	383	1370	390	159	7	16	18	4.5	131	0.28
KL32-05	708	711	0.189	1890	0.05	5.8	1000	2200	530	100	4	15	32	4.0	153	0.55
KL32-05	711	714	0.11	1100	0.03	1.6	1140	352	82	80	3	14	2.8	3.4	102	0.19
KL32-05	714	717	0.062	620	0.04	2	2310	630	160	275	1	15	2	5.5	107	0.3
KL32-05	717	720	0.078	780	0.03	0.01	310	219	67	108	1	6	2.6	2.3	80	0.01
KL32-05	720	723	0.149	1490	0.01	0.01	341	157	66	94	0.01	8	2.1	3.3	76	0.01
KL32-05	723	726	0.063	630	0.01	0.01	17	12	14	44	0.01	7	0.6	1.6	95	0.01
KL32-05	726	729	0.086	860	0.01	0.01	28	11	2	45	0.01	7	0.2	2.4	210	0.01
KL32-05	729	732	0.048	480	0.01	0.01	17	8	2	23	0.01	7	0.2	2.4	160	0.01
KL32-05	732	735	0.05	500	0.01	0.01	32	21	38	39	0.01	7	0.4	2.3	127	0.01
KL32-05	735	738	0.0299	299	0.01	0.01	153	151	50	108	0.01	5	3.6	1.1	201	0.01
KL32-05	738	741	0.126	1260	0.04	2.1	74	62	88	74	5	8	92	2.8	152	0.11
KL32-05	741	744	0.0351	351	0.01	0.01	50	33	9	110	0.01	8	0.9	1.3	280	0.01
KL32-05	744	747	0.042	420	0.01	0.01	49	49	9	77	0.01	14	1	2.4	148	0.01
KL32-05	747	750	0.0243	243	0.01	0.01	59	50	8	85	0.01	7	1.2	2.7	182	0.01
KL32-05	750	753	0.0345	345	0.01	0.01	27	21	4	79	0.01	16	0.3	3.4	220	0.01
KL32-05	753	756	0.058	580	0.01	0.01	53	33	8	133	2	19	0.5	3.2	223	0.01
KL32-05	756	759	0.21	2100	0.02	4.8	151	153	78	60	20	10	3	2.3	107	0.01
KL32-05	759	762	0.024	240	0.01	0.01	26	14	19	102	0.01	14	1.1	2.9	185	0.01
KL32-05	762	765	0.0161	161	0.01	0.01	19	22	1	116	0.01	10	0.01	2.6	139	0.01
KL32-05	765	768	0.0163	163	0.01	0.01	15	20	15	77	1	7	1.5	1.5	276	0.01
KL32-05	768	771	0.0133	133	0.01	0.01	24	45	23	90	0.01	11	1.1	1.6	267	0.01
KL32-05	771	774	0.0129	129	0.01	0.01	34	52	19	75	0.01	16	1.3	2.0	218	0.01
KL32-05	774	775.7	0.104	1040	0.03	6.1	128	135	340	111	1	15	26	3.2	220	0.23
KL32-06	0	2.5	0.0044	44	0.03	0.6	620	218	10	3	0.01	0.01	2.6	2.0	23	0.01
KL32-06	2.5	5.1	0.0029	29	0.01	0.01	213	56	9	3	0.01	0.01	1.4	1.1	22	0.01
KL32-06	5.1	8	0.0028	28	0.01	0.01	299	99	9	2	0.01	0.01	1.2	1.2	24	0.01
KL32-06	8	10.5	0.0016	16	0.01	0.01	137	37	9	0.01	0.01	0.01	0.9	0.8	22	0.01
KL32-06	10.5	12.8	0.002	20	0.01	0.01	174	38	6	0.01	0.01	0.01	1	0.6	22	0.01
KL32-06	12.8	15.5	0.0018	18	0.01	0.01	154	38	7	0.01	0.01	0.01	0.8	0.5	20	0.01
KL32-06	15.5	18.6	0.001	10	0.01	0.01	123	36	5	0.01	0.01	0.01	0.8	1.1	18	0.01
KL32-06	18.6	21.8	0.0012	12	0.01	0.01	150	47	9	0.01	0.01	0.01	1.1	1.0	20	0.01
KL32-06	21.8	24.6	0.0022	22	0.01	0.01	124	35	6	0.01	0.01	0.01	1	0.8	21	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL32-06	24.6	28	0.002		20	0.01	0.01	256	59	9	2	0.01	0.01	1.6	1.1	20	0.01
KL32-06	28	30.6	0.0016		16	0.02	0.01	308	75	6	0.01	0.01	0.01	1.4	1.1	26	0.01
KL32-06	30.6	33.6	0.0005		5	0.01	0.01	196	66	8	0.01	0.01	0.01	1	1.2	24	0.01
KL32-06	33.6	36.4	0.046		460	0.03	0.01	305	97	14	9	0.01	0.01	2.1	1.2	25	0.01
KL32-06	36.4	39.7	0.0068		68	0.02	0.01	1350	460	34	4	0.01	2	2.9	4.6	23	0.01
KL32-06	39.7	41.2	0.0104		104	0.03	0.01	490	122	20	6	0.01	0.01	1.7	1.1	34	0.01
KL32-06	41.2	43	0.0078		78	0.02	0.01	560	147	20	4	0.01	0.01	1.9	1.4	29	0.01
KL32-06	43	45.5	0.0029		29	0.01	0.01	490	167	32	0.01	0.01	3	1.7	2.6	16	0.01
KL32-06	45.5	47.5	0.008		80	0.01	0.01	146	61	22	3	0.01	0.01	1.8	0.9	17	0.01
KL32-06	47.5	50.5	0.0016		16	0.11	0.01	196	54	14	0.01	0.01	0.01	1.1	1.4	15	0.01
KL32-06	50.5	52.5	0.0021		21	0.01	0.01	106	90	22	0.01	0.01	0.01	1.5	1.3	16	0.01
KL32-06	52.5	54.8	0.0021		21	0.01	0.01	125	94	22	0.01	0.01	0.01	1.3	1.0	16	0.01
KL32-06	54.8	57.6	0.003		30	0.06	0.01	189	60	14	0.01	0.01	0.01	1.1	1.1	17	0.01
KL32-06	57.6	60.1	0.0067		67	0.06	0.01	169	56	20	4	0.01	2	2.2	1.4	19	0.01
KL32-06	60.1	62	0.0043		43	0.19	0.01	250	50	9	0.01	0.01	3	1.1	2.2	17	0.01
KL32-06	62	64	0.0082		82	0.22	0.8	600	183	23	15	1	0.01	4.3	2.0	30	0.01
KL32-06	64	66.4	0.0068		68	0.1	0.01	410	121	9	6	0.01	0.01	2.1	1.7	18	0.01
KL32-06	66.4	69.5	0.005		50	0.37	0.01	259	62	17	3	0.01	0.01	2.3	2.2	20	0.01
KL32-06	69.5	71.5	0.0016		16	0.42	0.01	196	47	14	2	0.01	0.01	1.2	1.9	18	0.01
KL32-06	71.5	74.5	0.0028		28	0.02	0.01	49	138	20	2	1	0.01	0.7	2.2	29	0.01
KL32-06	74.5	77.5	0.0011		11	0.05	0.6	69	269	18	3	1	0.01	1	4.0	20	0.01
KL32-06	77.5	81	0.0027		27	0.01	1	120	369	17	3	3	0.01	0.9	7.5	23	0.01
KL32-06	81	84	0.0021		21	0.01	5.1	420	1060	23	7	13	0.01	0.7	35.0	22	0.01
KL32-06	84	85.6	0.153		1530	0.03	70	23500	8500	64	51	401	3	3.1	352.0	26	0.1
KL32-06	85.6	86.6	0.56		5600	0.32	940	201000	91500	840	236	7200	12	50	3350.0	78	0.01
KL32-06	86.6	90.1	0.111		1110	0.16	156	32200	40200	210	86	560	2	32	430.0	29	0.36
KL32-06	90.1	93.1	0.0051		51	0.18	5.2	1100	1360	51	17	24	0.01	6.8	17.8	24	0.1
KL32-06	93.1	95.5	0.0104		104	1.05	15.2	1840	2800	130	9	44	0.01	22	44.0	30	0.11
KL32-06	95.5	97	0.002		20	0.27	0.7	49	120	13	2	3	0.01	6.8	4.5	19	0.01
KL32-06	97	100	0.0012		12	0.36	0.6	107	114	23	3	2	0.01	6.7	2.7	26	0.01
KL32-06	100	103	0.001		10	0.06	0.01	67	71	17	0.01	2	0.01	1	2.1	33	0.01
KL32-06	103	104.8	0.0025		25	0.4	0.9	119	142	29	0.01	3	0.01	1.1	3.7	31	0.01
KL32-06	104.8	107.8	0.0006		6	0.04	0.01	56	32	35	0.01	1	0.01	0.6	1.7	41	0.01
KL32-06	107.8	110.9	0.001		10	0.07	0.7	106	119	12	0.01	2	0.01	1.3	4.0	32	0.01
KL32-06	110.9	112	0.0075		75	0.05	0.01	96	50	13	0.01	0.01	0.01	1.8	3.6	26	0.1
KL32-06	112	115	0.0221		221	0.07	4.6	1300	650	48	19	0.01	0.01	7.4	14.9	44	0.19
KL32-06	115	118	0.0052		52	0.05	0.01	139	36	12	2	0.01	0.01	1.3	2.0	33	0.12
KL32-06	118	121	0.007		70	0.01	0.01	67	36	22	0.01	0.01	0.01	1	0.9	43	0.01
KL32-06	121	124	0.0054		54	0.04	0.01	74	38	14	4	0.01	0.01	1.2	2.5	23	0.1
KL32-06	124	127	0.0069		69	0.03	0.01	78	50	11	4	0.01	0.01	0.5	1.5	28	0.01
KL32-06	127	130	0.0084		84	0.01	0.01	128	72	18	2	0.01	3	1.3	2.3	25	0.01
KL32-06	130	133	0.0111		111	0.02	0.01	118	62	28	3	0.01	2	1.7	1.5	28	0.01
KL32-06	133	136	0.0211		211	0.05	0.7	284	111	43	7	0.01	2	4.7	1.9	34	0.01
KL32-06	136	139	0.0075		75	0.28	0.01	77	50	16	5	0.01	0.01	1.6	3.3	27	0.23
KL32-06	139	142	0.007		70	0.01	0.01	85	35	21	2	0.01	2	0.7	1.1	50	0.01
KL32-06	142	145	0.0086		86	0.01	0.01	96	36	21	4	0.01	4	0.9	0.8	50	0.01
KL32-06	145	148	0.0227		227	0.1	1	231	175	52	6	0.01	2	2	3.2	53	0.01
KL32-06	148	149.6	0.0128		128	0.03	0.01	130	85	27	4	0.01	2	1.3	3.0	37	0.01
KL32-06	149.6	154	0.0345		345	0.26	18	10400	13200	68	78	3	3	48	25.5	41	0.19
KL32-06	154	157	0.068		680	0.94	21.1	14000	14100	240	113	5	5	80	31.5	42	0.35
KL32-06	157	158.5	0.0302		302	0.17	19.1	10800	13600	71	11	4	3	56	28.8	34	0.18
KL32-06	158.5	162	0.0062		62	0.12	0.9	430	392	44	6	0.01	0.01	6.7	3.5	22	0.11
KL32-06	162	164	0.0134		134	0.19	0.6	480	410	27	3	0.01	0.01	8.1	3.5	32	0.01
KL32-06	164	167	0.0217		217	0.08	2.8	1100	1500	19	18	3	0.01	5	11.8	26	0.01
KL32-06	167	168.5	0.0193		193	0.01	0.01	69	58	8	8	0.01	0.01	4.3	0.0	24	0.01
KL32-06	168.5	169.5	0.0196		196	0.04	1.7	389	570	13	5	5	2	6.1	4.9	31	0.01
KL32-06	169.5	172.5	0.014		140	0.21	1.8	296	298	39	8	0.01	0.01	9.5	5.3	27	0.1
KL32-06	172.5	175.5	0.0151		151	0.24	0.5	171	138	27	7	0.01	0.01	3.2	2.4	26	0.01
KL32-06	175.5	178	0.067		670	0.21	13.8	2800	1660	130	60	54	6	42	48.0	105	0.57
KL32-06	178	180.8	0.0204		204	0.04	0.9	226	158	30	11	5	0.01	3.8	1.0	29	0.01
KL32-06	180.8	183.7	0.0184		184	0.05	1.4	410	250	32	12	6	0.01	5.4	2.6	22	0.1
KL32-06	183.7	186.2	0.0189		189	0.05	1.4	860	140	45	42	19	0.01	6.7	14.1	21	0.01
KL32-06	186.2	189.1	0.0227		227	0.04	1.2	480	428	27	9	11	0.01	4.2	2.1	24	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL32-06	189.1	192.4	0.029		290	0.07	1.7	660	315	63	17	9	2	4.9	3.6	22	0.1
KL32-06	192.4	194.9	0.0167		167	0.05	0.6	336	129	29	15	3	0.01	2.4	1.3	19	0.01
KL32-06	194.9	198.9	0.0224		224	0.37	2.8	1060	710	73	21	6	2	12.2	4.7	30	0.14
KL32-06	198.9	202	0.0283		283	1.67	2.5	1720	640	180	500	15	3	48	12.0	32	0.35
KL32-06	202	205	0.0081		81	0.64	2.5	321	230	110	151	30	9	11.7	17.3	120	0.17
KL32-06	205	208	0.0048		48	0.64	1.3	337	105	130	84	4	2	7.7	4.6	126	0.14
KL32-06	208	210.4	0.0351		351	0.36	8.4	3500	5200	100	267	5	4	28	17.8	36	0.12
KL32-06	210.4	212.9	0.128		1280	0.51	5.1	1700	1720	170	528	6	6	14.6	11.3	40	0.23
KL32-06	212.9	215.3	0.0115		115	0.7	3.2	2500	520	220	1210	12	11	13.3	20.0	114	0.37
KL32-06	215.3	219.1	0.041		410	2.26	5.2	2400	910	300	1410	31	6	50	18.0	65	0.51
KL32-06	219.1	221.7	0.0319		319	0.85	1.7	1040	246	110	632	7	3	32	9.8	38	0.27
KL32-06	221.7	223.9	0.0138		138	3.07	1.9	710	266	250	1720	7	6	24	13.5	88	0.66
KL32-06	223.9	227	0.047		470	2.5	4.3	2300	970	260	1190	18	7	75	18.8	37	0.45
KL32-06	227	230.1	0.0314		314	0.77	8.2	3800	1090	140	346	10	6	44	13.8	26	0.22
KL32-06	230.1	233	0.0151		151	0.33	4.1	1770	500	48	100	4	3	9.4	6.3	30	0.1
KL32-06	233	236.3	0.045		450	0.58	5.5	3400	690	110	104	6	7	15.3	10.0	28	0.34
KL32-06	236.3	239	0.0198		198	0.3	6.8	3600	1010	75	106	6	2	13.2	8.3	27	0.32
KL32-06	239	242	0.061		610	0.65	14.7	5100	2400	120	270	16	4	45	18.3	28	0.34
KL32-06	242	245.1	0.22		2200	1.04	83	37100	12500	500	546	33	25	116	33.0	61	0.84
KL32-06	245.1	248.5	0.23		2300	0.7	32.6	12900	1870	440	236	15	21	352	17.5	32	0.33
KL32-06	248.5	251.1	0.7		7000	0.72	118	22100	6300	1980	220	30	20	1375	16.8	48	0.56
KL32-06	251.1	253.2	0.046		460	0.27	2.1	2600	630	130	37	3	6	33	5.8	31	0.1
KL32-06	253.2	255.4	2.35		23500	2.49	34	49000	2500	2900	2750	101	110	530	61.5	61	0.4
KL32-06	255.4	258.4	0.065		650	0.82	2.5	3300	500	220	186	8	12	30	15.5	36	0.27
KL32-06	258.4	261.2	0.041		410	0.62	2.2	2100	400	150	60	5	6	9.4	8.5	21	0.18
KL32-06	261.2	263.8	0.35		3500	0.66	56	12200	3600	980	166	22	13	630	19.5	37	0.51
KL32-06	263.8	265	1.08		10800	2.77	13.3	11300	420	2010	419	8	51	13.8	31.9	77	1.76
KL32-06	265	268	0.251		2510	1.75	3.4	4900	470	380	156	3	16	9.2	18.5	31	1.84
KL32-06	268	271	0.34		3400	3.16	6.4	8400	267	350	195	4	21	6.8	17.5	32	3.29
KL32-06	271	274	0.394		3940	1.93	6.4	4300	1200	340	146	5	19	10.4	25.0	34	2.25
KL32-06	274	277	0.478		4780	1.89	9.4	4800	1600	520	158	20	19	17.8	25.4	40	1.7
KL32-06	277	280	0.111		1110	0.77	9.5	3100	1030	420	210	32	8	35	30.1	32	0.77
KL32-06	280	283	2.16		21600	1.67	31	8600	5800	660	173	4	54	46	48.0	43	0.95
KL32-06	283	286	0.7		7000	0.81	40	18500	21600	320	254	34	21	36	54.0	67	0.74
KL32-06	286	289	0.207		2070	1.91	22.1	13700	13600	200	167	6	11	35	53.0	35	1.54
KL32-06	289	292	0.057		570	0.83	12.7	6200	3100	130	103	10	6	26	52.0	32	0.28
KL32-06	292	295	0.166		1660	0.84	14.5	6900	3600	320	128	10	9	78	54.0	33	0.26
KL32-06	295	298.8	0.207		2070	0.62	11.8	5000	2800	390	126	9	10	125	29.5	29	0.23
KL32-06	298.8	301	0.0277		277	0.23	3.2	1930	1210	83	75	3	0.01	15.9	8.5	25	0.01
KL32-06	301	303.9	0.044		440	0.14	3.6	2000	1030	120	62	3	2	60	7.0	27	0.01
KL32-06	303.9	307	0.055		550	0.35	5.1	2500	1090	170	71	4	3	70	8.3	25	0.01
KL32-06	307	310	0.0188		188	0.4	3.5	1120	670	61	67	3	0.01	10.8	6.5	24	0.01
KL32-06	310	312.7	0.0141		141	0.18	1.6	580	162	35	74	3	2	5.4	3.3	23	0.01
KL32-06	312.7	316.1	0.107		1070	0.39	9.7	3300	1090	300	336	6	8	68	22.2	32	0.15
KL32-06	316.1	318.5	0.22		2200	1.27	23.4	5800	2300	540	384	18	17	95	49.0	37	0.22
KL32-06	318.5	321.6	0.0189		189	0.34	5.7	2570	1760	84	57	7	3	14.6	38.5	31	0.01
KL32-06	321.6	324.7	0.0256		256	0.47	7.1	5400	1720	78	86	8	4	14	35.0	37	0.11
KL32-06	324.7	327.7	0.0281		281	0.46	5.9	6700	1450	91	92	10	5	11.3	26.5	49	0.12
KL32-06	327.7	330.6	0.0092		92	0.16	2.1	810	327	39	37	4	3	5.7	12.0	30	0.01
KL32-06	330.6	333.6	0.0081		81	0.24	2.3	1070	242	35	39	5	3	3.7	18.5	30	0.01
KL32-06	333.6	336.6	0.0161		161	0.3	4	1700	1200	58	51	5	2	8.9	23.5	30	0.1
KL32-06	336.6	339.6	0.052		520	0.08	1.2	1010	145	28	224	5	4	5.2	7.3	30	0.01
KL32-06	339.6	342.6	0.0317		317	0.16	1.6	1230	158	28	146	5	4	5	13.5	27	0.01
KL32-06	342.6	345	0.0341		341	0.07	1	660	149	22	227	3	6	2.7	8.8	33	0.01
KL32-06	345	347.5	0.0192		192	0.05	0.01	610	74	15	136	3	3	2.3	8.8	18	0.01
KL32-06	347.5	349	0.0161		161	0.05	1.2	1430	150	50	78	32	2	3.4	21.5	18	0.01
KL32-06	349	352	0.0081		81	0.27	0.8	371	149	32	31	12	3	2.8	19.2	21	0.1
KL32-06	352	355	0.007		70	0.33	0.6	284	132	30	26	7	3	3.6	15.0	20	0.12
KL32-06	355	358	0.0083		83	0.29	1.6	650	540	160	41	2	2	6	14.5	33	0.16
KL32-06	358	361	0.0077		77	0.24	2.5	700	700	140	43	2	5	9.9	14.3	36	0.18
KL32-06	361	364	0.005		50	0.47	3.9	820	850	120	18	0.01	3	16.8	16.0	43	0.33
KL32-06	364	367	0.006		60	0.46	4.3	1020	920	110	19	1	3	11.9	16.9	43	0.37
KL32-06	367	370	0.0032		32	0.63	1.3	314	258	40	7	0.01	2	11.9	9.8	29	0.25

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL32-06	370	373	0.0048		48	0.35	1.7	341	351	69	28	1	4	13.5	11.0	38	0.27
KL32-06	373	376	0.0036		36	0.25	1.5	178	130	45	8	0.01	6	7.4	5.3	21	0.15
KL32-06	376	379	0.0071		71	0.21	1.4	277	248	34	7	0.01	6	4.8	4.5	24	0.17
KL32-06	379	382	0.0032		32	0.37	0.9	279	187	31	6	0.01	5	7.2	5.0	28	0.11
KL32-06	382	385	0.0124		124	0.56	2.3	530	289	64	15	0.01	3	15.5	10.0	29	0.15
KL32-06	385	388	0.0103		103	0.21	3.2	660	630	63	15	3	5	5.8	7.8	32	0.1
KL32-06	388	391	0.0042		42	0.15	1.6	231	166	22	5	0.01	0.01	1.3	4.8	25	0.01
KL32-06	391	394	0.0093		93	0.49	7	660	510	65	8	1	0.01	11.7	17.8	36	0.11
KL32-06	394	397	0.0035		35	0.2	1.9	207	163	33	6	0.01	0.01	3.1	7.8	28	0.01
KL32-06	397	400	0.058		580	0.44	5.9	2190	750	170	74	6	3	53	10.0	29	0.2
KL32-06	400	403	0.0026		26	0.24	1.2	291	281	30	8	0.01	0.01	2.7	6.2	27	0.1
KL32-06	403	406	0.0104		104	0.46	7.5	750	460	87	8	0.01	0.01	16.3	17.5	34	0.18
KL32-06	406	409	0.0306		306	0.26	15.6	6600	2700	40	41	15	0.01	17.4	14.0	30	0.27
KL32-06	409	412	0.002		20	0.34	0.6	243	153	24	3	1	0.01	4.9	5.3	30	0.1
KL32-06	412	415	0.0027		27	0.42	1.1	240	167	17	5	0.01	0.01	7.6	4.3	28	0.01
KL32-06	415	418	0.061		610	0.64	15.4	6400	7800	100	57	4	4	18.8	36.5	35	0.45
KL32-06	418	421	0.0055		55	0.35	1	365	334	22	5	0.01	0.01	10.6	4.8	25	0.1
KL32-06	421	424	0.0135		135	0.4	1.9	920	910	32	8	1	0.01	9.6	7.8	27	0.11
KL32-06	424	427	0.0068		68	0.36	1.7	600	292	32	76	1	4	6.7	12.5	34	0.01
KL32-06	427	430	0.0027		27	0.25	1.5	367	269	19	3	0.01	0.01	6	6.3	29	0.01
KL32-06	430	433	0.0038		38	0.2	1.3	345	178	21	25	0.01	0.01	5.7	3.8	26	0.01
KL32-06	433	435.7	0.0021		21	0.23	1.6	274	255	20	2	0.01	3	3.8	5.8	24	0.01
KL32-07	0	2	0.0014		14	0.04	0.01	194	66	7	4	0.01	0.01	1.1	1.2	28	0.01
KL32-07	2	5.3	0.0014		14	0.01	0.01	105	50	5	3	0.01	0.01	0.5	1.0	31	0.01
KL32-07	5.3	7.5	0.0009		9	0.01	0.8	169	98	6	2	0.01	0.01	0.7	1.1	34	0.01
KL32-07	7.5	10.5	0.0029		29	0.02	0.7	165	93	14	3	3	0.01	0.6	2.0	31	0.01
KL32-07	10.5	13.5	0.0034		34	0.01	0.9	420	325	13	3	1	0.01	0.6	1.9	24	0.01
KL32-07	13.5	16.5	0.0019		19	0.02	0.01	122	45	6	0.01	0.01	0.01	1.3	0.6	18	0.01
KL32-07	16.5	19.5	0.0016		16	0.02	0.8	234	87	9	3	1	0.01	0.6	1.9	25	0.01
KL32-07	19.5	22.5	0.0055		55	0.03	0.01	158	67	5	3	0.01	0.01	0.5	1.2	16	0.01
KL32-07	22.5	23.6	0.0063		63	0.11	0.9	309	130	8	3	0.01	0.01	0.7	3.5	20	0.01
KL32-07	23.6	26.3	0.0019		19	0.04	1.3	670	294	14	3	0.01	0.01	0.8	5.5	17	0.01
KL32-07	26.3	28.5	0.003		30	0.06	1.2	375	336	25	7	0.01	0.01	2.3	3.0	27	0.01
KL32-07	28.5	31.5	0.0034		34	0.06	1.8	279	1200	20	6	0.01	0.01	1.6	1.5	28	0.01
KL32-07	31.5	34.5	0.0057		57	0.28	3.3	520	1680	23	8	6	0.01	2.2	4.8	30	0.01
KL32-07	34.5	37.5	0.01		100	0.09	9	1670	5500	28	22	23	0.01	5	18.3	18	0.01
KL32-07	37.5	40.5	0.0208		208	0.18	23.8	2900	3920	32	16	64	0.01	2.7	47.0	24	0.01
KL32-07	40.5	43.5	0.0017		17	0.01	1.2	236	1120	16	9	1	0.01	1.3	2.2	18	0.01
KL32-07	43.5	46.5	0.0058		58	0.04	3.3	520	780	31	13	6	0.01	2.7	2.0	22	0.01
KL32-07	46.5	49.5	0.0092		92	0.26	9.1	2140	3320	60	8	1	0.01	18.7	12.5	21	0.01
KL32-07	49.5	52.5	0.0348		348	0.23	10.1	1980	1810	130	16	30	0.01	50	7.3	25	0.01
KL32-07	52.5	55.5	0.0015		15	0.1	0.7	228	460	27	0.01	0.01	0.01	9	2.8	21	0.01
KL32-07	55.5	58.5	0.0041		41	0.06	1.4	1070	860	33	6	0.01	0.01	2.6	4.5	24	0.01
KL32-07	58.5	61.5	0.0044		44	0.23	1.7	366	340	81	8	3	0.01	6.8	7.0	34	0.14
KL32-07	61.5	64.5	0.005		50	0.44	1.5	314	314	85	9	5	0.01	3.2	6.0	27	0.1
KL32-07	64.5	67.5	0.0035		35	0.51	2.7	558	460	73	4	5	0.01	4.6	2.3	30	0.39
KL32-07	67.5	70.5	0.004		40	0.64	2.3	281	268	90	10	4	0.01	4.2	5.0	28	0.61
KL32-07	70.5	73.5	0.0062		62	0.5	1.8	470	238	42	38	7	0.01	2.5	3.7	33	0.43
KL32-07	73.5	75	0.0101		101	0.1	2.5	644	680	80	32	9	0.01	3.1	2.5	24	0.01
KL32-07	75	78	0.057		570	0.54	10.9	10300	7400	160	75	7	3	24	23.3	110	0.56
KL32-07	78	81	0.74		7400	1.29	2.4	212	65	5	12	0.01	15	0.01	3.5	107	0.01
KL32-07	81	84.2	0.102		1020	0.59	9.8	12000	3200	710	28	7	8	43	22.8	72	0.89
KL32-07	84.2	89.3	0.0361		361	0.21	4.3	1880	1450	120	27	6	3	9.8	9.8	79	0.16
KL32-07	89.3	91.3	0.0223		223	0.48	2.8	325	260	130	33	2	0.01	8.6	5.3	99	0.39
KL32-07	91.3	94.5	0.051		510	0.62	6.8	6000	1330	190	17	14	2	18	12.8	154	0.59
KL32-07	94.5	97.5	1.58		15800	0.23	43	4650	2000	4200	8	32	0.01	167	2.5	120	0.93
KL32-07	97.5	100.5	0.095		950	0.2	7.8	4500	1710	290	9	13	2	14.8	5.5	182	0.22
KL32-07	100.5	103.5	0.011		110	0.52	5.2	8300	3600	110	10	8	0.01	9.3	17.0	112	0.41
KL32-07	103.5	106.5	0.0174		174	0.25	14	3830	5900	120	18	40	0.01	7.5	14.0	103	0.27
KL32-07	106.5	109.5	0.0044		44	0.33	2.4	2290	570	100	18	3	0.01	4.3	6.8	99	0.36
KL32-07	109.5	112.5	0.0118		118	0.12	2.3	3300	970	65	7	10	0.01	4.5	1.8	52	0.1
KL32-07	112.5	115.5	0.0049		49	0.04	1.1	147	78	37	21	5	3	1.9	3.0	91	0.01
KL32-07	115.5	118.5	0.0325		325	0.03	1.2	94	148	58	67	6	5	7.8	1.8	69	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL32-07	118.5	121.5	0.197		1970	0.18	3.2	159	175	160	82	23	15	6.5	8.3	45	0.01
KL32-07	121.5	124.5	0.028		280	0.07	1.6	174	214	110	17	41	9	6.2	5.0	21	0.01
KL32-07	124.5	127.5	0.0138		138	0.07	2.7	730	392	93	7	32	2	2.7	3.8	22	0.01
KL32-07	127.5	128.35	0.0075		75	0.03	9.7	2530	880	17	129	24	0.01	0.7	9.0	21	0.01
KL32-07	128.35	129.4	0.75		7500	0.2	192	35600	22400	1810	162	600	20	44	90.0	75	0.65
KL32-07	129.4	130.5	0.123		1230	0.04	37	47100	31900	100	35	28	0.01	30	26.0	26	0.22
KL32-07	130.5	133.5	0.4		4000	0.15	93	132000	74900	390	178	70	0.01	80	76.0	50	0.46
KL32-07	133.5	135.2	0.055		550	0.06	26.7	18000	19200	47	25	26	0.01	13.7	23.9	20	0.24
KL32-07	135.2	137.8	0.32		3200	0.29	181	141000	143000	360	24	59	0.01	143	105.5	61	0.97
KL32-07	137.8	140.6	0.0244		244	0.05	23.8	10700	7200	38	31	26	0.01	6.1	16.0	19	0.16
KL32-07	140.6	142	0.104		1040	0.27	78	42200	37000	210	23	71	0.01	35	63.0	53	0.58
KL32-07	142	144.2	0.21		2100	0.35	95	74200	55700	320	12	94	0.01	45	60.0	52	0.73
KL32-07	144.2	147.7	0.04		400	0.06	32.5	29300	18200	52	11	30	0.01	12.8	11.0	21	0.19
KL32-07	147.7	148.5	0.0064		64	0.04	12.7	620	2400	18	17	22	0.01	1	5.3	18	0.01
KL32-07	148.5	151.5	0.0174		174	0.03	13.2	5920	4840	33	17	20	0.01	2.5	6.3	21	0.01
KL32-07	151.5	154.5	0.0409		409	0.04	27.8	10500	5100	60	117	46	0.01	7.5	23.0	19	0.01
KL32-07	154.5	157.5	0.0054		54	0.03	4.3	353	352	10	116	25	0.01	0.5	5.0	23	0.01
KL32-07	157.5	160.3	0.056		560	0.08	38	6400	6300	100	107	113	0.01	8.1	15.8	37	0.16
KL32-07	160.3	163.3	0.0035		35	0.02	12.7	710	1170	17	24	32	0.01	0.3	6.0	24	0.01
KL32-07	163.3	166.3	0.0056		56	0.05	6.4	800	1160	23	19	14	0.01	0.7	4.8	23	0.01
KL32-07	166.3	169.4	0.0142		142	0.03	8.1	6920	3500	31	6	14	0.01	3	11.0	25	0.01
KL32-07	169.4	172	0.0063		63	0.02	7	1160	830	17	8	13	0.01	0.5	3.8	24	0.01
KL32-07	172	175.5	0.0105		105	0.02	10.4	2980	1420	22	4	23	0.01	0.9	4.5	23	0.01
KL32-07	175.5	178.2	0.027		270	0.07	26.7	17800	13700	120	6	38	0.01	16.1	12.0	26	0.16
KL32-07	178.2	181.5	0.0051		51	0.02	3.1	1680	740	17	10	8	0.01	1.1	2.5	25	0.01
KL32-07	181.5	182.9	0.003		30	0.03	0.8	270	202	12	8	1	0.01	0.3	1.0	24	0.01
KL32-07	182.9	184.5	0.0078		78	0.04	1.9	1080	700	44	10	2	0.01	2.3	1.3	33	0.01
KL32-07	184.5	187.9	0.013		130	0.01	3.2	1510	2310	21	21	0.01	0.01	3.7	1.8	23	0.01
KL32-07	187.9	190.5	0.0094		94	0.02	6	2500	3800	33	13	0.01	0.01	5	2.8	22	0.01
KL32-07	190.5	193.5	0.0123		123	0.32	16.8	5250	9400	3000	8	4	0.01	60	14.3	17	1.05
KL32-07	193.5	196.5	0.0154		154	0.08	7.2	3660	5700	58	9	10	0.01	4.2	11.0	23	0.01
KL32-07	196.5	199.5	0.009		90	0.01	2.4	3150	2830	35	65	0.01	0.01	2.6	3.5	20	0.01
KL32-07	199.5	201	0.0091		91	0.01	4.5	1260	6200	28	28	2	0.01	3.7	12.3	19	0.01
KL32-07	201	204	0.0085		85	0.01	5.5	2960	5200	17	7	1	0.01	4.1	8.5	15	0.01
KL32-07	204	207	0.0027		27	0.01	2	1310	2610	7	5	1	0.01	2.2	2.5	14	0.01
KL32-07	207	210	0.0055		55	0.03	2.7	930	970	9	7	6	0.01	1.5	4.3	14	0.01
KL32-07	210	213	0.0048		48	0.01	1.8	1200	1310	14	6	3	0.01	1	2.3	12	0.01
KL32-07	213	216	0.0133		133	0.01	11.2	4700	12300	11	14	5	0.01	16.1	11.0	15	0.01
KL32-07	216	218.9	0.0055		55	0.01	3.3	7300	3500	10	8	2	0.01	2.2	9.3	16	0.01
KL32-07	218.9	222	0.0057		57	0.05	4.4	3230	3120	34	16	7	0.01	3	8.5	18	0.1
KL32-07	222	225	0.0184		184	0.04	57	20500	60000	32	8	7	0.01	50	29.5	15	0.11
KL32-07	225	228	0.0032		32	0.02	1	543	650	6	10	2	0.01	2.2	2.3	16	0.01
KL32-07	228	230.2	0.0024		24	0.04	1.8	1290	1280	7	3	0.01	0.01	2.8	3.5	16	0.01
KL32-07	230.2	231.7	0.0052		52	0.01	3.3	2200	3840	12	2	2	0.01	2.9	7.0	11	0.01
KL32-07	231.7	234.2	0.0053		53	0.12	4	4730	2840	40	4	4	0.01	5.1	10.5	12	0.33
KL32-07	234.2	237.3	0.0143		143	0.15	7.2	11700	3200	47	6	5	0.01	7.2	10.0	14	1.14
KL32-07	237.3	239.9	0.0034		34	0.03	0.01	780	480	9	7	2	0.01	1	1.9	16	0.01
KL32-07	239.9	242.9	0.001		10	0.03	0.6	375	343	9	2	0.01	0.01	0.8	1.1	13	0.01
KL32-07	242.9	244.5	0.0018		18	0.02	1.4	660	960	8	6	0.01	0.01	0.01	2.3	15	0.01
KL32-07	244.5	247.5	0.0014		14	0.02	1.2	780	930	6	4	0.01	0.01	1.3	1.5	12	0.01
KL32-07	247.5	250.5	0.001		10	0.01	0.6	265	279	5	5	0.01	0.01	0.01	1.4	15	0.01
KL32-07	250.5	253.5	0.0166		166	0.08	6.4	4440	7900	26	13	2	0.01	5	8.6	13	0.01
KL32-07	253.5	256.5	0.0054		54	0.04	1.8	990	1420	14	11	1	0.01	2.8	2.7	16	0.01
KL32-07	256.5	259.5	0.0095		95	0.16	0.9	394	540	48	21	0.01	0.01	0.01	3.3	27	0.01
KL32-07	259.5	262.5	0.0034		34	0.05	1.2	352	500	16	10	2	0.01	1	3.5	19	0.01
KL32-07	262.5	265.5	0.0035		35	0.04	1.7	910	750	13	8	4	0.01	1.2	4.0	16	0.01
KL32-07	265.5	268.5	0.0143		143	0.08	3.5	1970	2780	27	19	4	0.01	1.7	7.4	15	0.01
KL32-07	268.5	271.5	0.0059		59	0.02	1.2	480	520	12	9	2	0.01	1	3.3	17	0.01
KL32-07	271.5	274	0.0061		61	0.02	1.4	490	510	13	8	2	0.01	1.3	3.0	18	0.01
KL32-07	274	276.8	0.0145		145	0.03	2.2	1030	640	19	6	4	0.01	4.7	5.0	17	0.01
KL32-07	276.8	279	0.004		40	0.02	1.1	229	281	13	14	2	0.01	1.8	3.3	16	0.01
KL32-07	279	282	0.0147		147	0.11	2.7	3290	930	27	18	4	2	2.7	6.5	17	0.3
KL32-07	282	285	0.0049		49	0.03	0.7	382	210	12	13	2	0.01	1	2.3	14	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL32-07	285	288	0.0271		271	0.1	1.5	315	146	29	18	3	0.01	1.7	2.8	22	0.01
KL32-07	288	289.5	0.341		3410	0.39	9.1	3960	550	33	57	25	12	1.7	8.4	18	0.01
KL32-07	289.5	292.5	1.06		10600	0.21	7.8	1210	620	18	1300	23	25	1.6	13.3	83	0.01
KL32-07	292.5	294.7	0.095		950	0.05	2.1	344	154	10	990	5	7	2.1	3.0	74	0.01
KL32-07	294.7	297	0.0254		254	0.02	1.4	159	80	5	1440	7	0.01	0.5	3.3	42	0.01
KL32-07	297	300	0.59		5900	0.21	17.8	19900	1360	54	362	41	45	1.8	18.0	21	0.01
KL32-07	300	301.2	0.62		6200	0.18	30.1	18400	1720	49	56	109	46	0.8	21.0	33	0.01
KL32-07	301.2	303.2	0.86		8600	0.99	15.2	4400	700	35	32	45	50	2.3	14.5	18	0.01
KL32-07	303.2	306	0.91		9100	0.32	37	13400	1490	86	205	240	71	3.1	24.0	50	0.01
KL32-07	306	309	0.185		1850	0.08	4.2	920	206	51	419	139	6	0.6	7.8	27	0.01
KL32-07	309	312	0.17		1700	0.05	3.5	1170	162	51	98	63	7	0.9	5.0	22	0.01
KL32-07	312	315	0.146		1460	0.15	3.4	1990	118	37	35	54	10	0.9	5.0	15	0.01
KL32-07	315	316.8	1.18		11800	1.17	22.5	1320	570	220	205	20	86	4.8	28.0	18	0.01
KL32-07	316.8	319.5	0.56		5600	0.15	5.4	9100	108	40	12	15	41	1.2	17.0	19	0.01
KL32-07	319.5	322.5	0.0396		396	0.08	1.1	304	21	18	660	6	6	0.6	4.4	12	0.01
KL32-07	322.5	325.5	0.046		460	0.16	1.7	740	57	18	520	4	7	0.9	11.0	16	0.01
KL32-07	325.5	328.5	0.77		7700	3.84	7.8	1050	256	73	390	14	59	2.2	25.8	35	0.01
KL32-07	328.5	331.5	1.41		14100	1.64	12	1130	47	38	12	55	84	2.3	45.0	58	0.01
KL32-07	331.5	334.5	1.27		12700	1.6	6.6	18400	47	39	7	65	52	1.3	41.5	28	0.01
KL32-07	334.5	336.4	1.68		16800	1.56	6.8	420	53	23	9	7	47	1.4	44.0	26	0.01
KL32-07	336.4	339.2	2.32		23200	1.64	7.3	450	41	30	12	7	43	1.1	28.0	49	0.01
KL32-07	339.2	342	3.48		34800	3.2	5.3	740	26	3	10	5	42	0.3	49.0	30	0.01
KL32-07	342	345	3.38		33800	4.87	5.7	710	19	2	4	4	45	0.3	37.0	26	0.01
KL32-07	345	348	5.6		56000	17.2	11.4	610	36	64	7	5	50	0.5	32.5	40	0.01
KL32-07	348	349.5	2.09		20900	2.12	8.4	146	11	9	9	1	60	0.2	17.0	81	0.01
KL32-07	349.5	352.5	1.29		12900	0.53	4.1	1580	2200	12	87	1	31	0.9	16.5	98	0.16
KL32-07	352.5	354	2.41		24100	0.76	5.8	960	1500	8	72	0.01	39	0.7	14.0	86	0.01
KL32-07	354	355.9	4.06		40600	0.93	10.9	397	144	41	86	5	54	3.9	20.0	95	0.12
KL32-07	355.9	357.7	2.65		26500	0.52	12	1420	730	130	110	0.01	21	25	30.0	105	0.46
KL32-07	357.7	360	2.16		21600	0.43	6	112	88	36	120	0.01	41	1.8	13.0	79	0.01
KL32-07	360	363	1.14		11400	0.43	1.7	191	40	7	82	0.01	22	0.6	8.5	86	0.01
KL32-07	363	366	1.03		10300	0.37	2.3	116	128	7	159	0.01	41	0.9	9.7	83	0.01
KL32-07	366	369	1.82		18200	0.63	3	186	142	5	168	0.01	55	0.9	15.0	84	0.01
KL32-07	369	372	2.04		20400	0.69	3.5	120	21	4	258	0.01	72	0.4	13.0	71	0.01
KL32-07	372	375	2		20000	0.55	4.5	89	17	2	94	0.01	80	0.2	17.0	67	0.01
KL32-07	375	378	1.46		14600	0.49	6.4	141	48	4	88	0.01	47	0.2	14.0	92	0.01
KL32-07	378	381	0.83		8300	0.37	5.2	104	11	10	34	2	12	0.01	7.8	93	0.01
KL32-07	381	384	1.11		11100	0.59	4.9	640	180	7	38	4	31	0.7	10.5	86	0.01
KL32-07	384	386	1.06		10600	0.57	2.7	58	18	4	153	0.01	22	0.4	9.5	95	0.01
KL32-07	386	387.9	1.31		13100	0.7	3.8	134	34	6	62	2	21	0.3	8.0	107	0.01
KL32-07	387.9	390	0.9		9000	0.61	2.4	208	41	5	10	2	11	0.3	8.0	86	0.01
KL32-07	390	393	0.93		9300	0.44	1.7	71	20	3	13	0.01	9	0.4	6.3	81	0.01
KL32-07	393	396	0.415		4150	0.19	1.9	520	70	18	39	2	13	0.8	8.0	61	0.01
KL32-07	396	399	0.79		7900	0.36	3.4	104	31	4	20	1	11	0.4	7.3	119	0.01
KL32-07	399	402	0.72		7200	0.27	2.3	70	20	4	42	1	10	0.2	6.3	82	0.01
KL32-07	402	405	0.985		9850	0.27	2.7	135	43	9	52	0.01	14	0.7	5.5	83	0.01
KL32-07	405	408	0.79		7900	0.28	2.1	970	48	6	84	4	12	0.3	6.3	76	0.01
KL32-07	408	411	0.84		8400	0.34	1.8	81	16	3	50	0.01	14	0.4	4.1	84	0.01
KL32-07	411	414	0.81		8100	0.35	1.2	58	10	2	71	0.01	10	0.8	6.3	75	0.01
KL32-07	414	416.4	1.6		16000	0.49	8.8	181	80	12	25	6	7	0.8	8.5	62	0.01
KL32-07	416.4	418.6	0.72		7200	0.37	1.5	249	38	4	22	1	11	0.7	6.3	77	0.01
KL32-07	418.6	420	1.59		15900	0.69	3.7	79	22	2	22	0.01	12	0.4	5.5	81	0.01
KL32-07	420	423	2.39		23900	1.02	10.4	1410	540	46	28	15	18	6.0	7.5	48	0.36
KL32-07	423	426	1.22		12200	0.51	5.5	151	24	7	65	8	18	2.7	8.0	65	0.01
KL32-07	426	428.1	0.94		9400	0.17	3.3	224	127	13	48	2	10	2	4.3	223	0.01
KL32-07	428.1	430.2	1.67		16700	0.51	2.5	97	37	4	43	1	12	0.7	6.5	112	0.01
KL32-07	430.2	432	0.486		4860	0.18	1.3	88	115	32	21	1	6	4.6	6.0	37	0.01
KL32-07	432	435	0.499		4990	0.16	1.3	113	90	24	100	2	3	12.6	5.0	29	0.01
KL32-07	435	438	0.464		4640	0.11	1.7	140	108	14	25	3	4	2.1	5.3	44	0.01
KL32-07	438	441	0.87		8700	0.41	1.6	126	73	19	129	1	6	5.5	6.8	50	0.01
KL32-07	441	444	1.28		12800	0.8	1.9	64	24	9	285	1	10	2.5	10.0	65	0.01
KL32-07	444	447	0.94		9400	0.4	2.4	163	89	6	32	1	8	1.7	5.8	53	0.01
KL32-07	447	450	1.12		11200	0.45	3	2560	730	10	40	2	7	5	6.0	164	0.26

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL32-07	450	453	1.13	11300	0.42	4.4	258	109	230	12	5	6	4.8	7.0	195	0.01
KL32-07	453	456	0.75	7500	0.35	3.3	112	78	150	32	3	5	2.2	4.8	135	0.01
KL32-07	456	459	0.66	6600	0.25	1.7	240	680	23	12	4	2	0.8	5.3	62	0.01
KL32-07	459	462	0.72	7200	0.34	2	67	67	160	11	3	0.01	1.4	4.8	37	0.01
KL32-07	462	465	0.82	8200	0.41	2	57	68	140	14	3	3	5.1	5.3	48	0.01
KL32-07	465	468	0.527	5270	0.32	1.4	46	121	130	24	2	4	1	5.8	38	0.01
KL32-07	468	471	0.82	8200	0.27	1.7	50	68	530	22	4	3	4.3	4.8	45	0.01
KL32-07	471	473.2	0.324	3240	0.11	1.6	166	174	250	74	2	3	3.5	2.3	31	0.01
KL32-07	473.2	476.2	0.432	4320	0.16	2.6	121	87	110	41	4	4	32	3.0	36	0.01
KL32-07	476.2	479.2	0.331	3310	0.18	1.1	62	67	61	24	2	2	4.6	2.0	42	0.01
KL32-07	479.2	483	0.54	5400	0.35	2.1	31	176	300	25	4	3	1.4	2.5	43	0.01
KL32-07	483	486	0.378	3780	0.22	1.7	95	80	5	29	2	3	1.1	1.5	49	0.01
KL32-07	486	489	0.448	4480	0.27	1.9	93	191	21	32	3	4	1.3	2.0	44	0.01
KL32-07	489	492	1.07	10700	0.55	4.1	71	50	13	151	3	6	0.7	7.0	66	0.01
KL32-07	492	494.5	0.75	7500	0.47	2.6	790	3200	13	20	4	4	1.4	2.0	62	0.01
KL32-07	494.5	496.4	0.65	6500	0.57	1.5	49	36	3	18	2	6	0.3	1.5	50	0.01
KL32-07	496.4	498	0.92	9200	0.66	2.7	50	32	6	63	2	5	0.5	2.8	61	0.01
KL32-07	498	501	0.403	4030	0.15	2.7	238	154	10	64	2	6	1.4	6.5	192	0.01
KL32-07	501	504	1.07	10700	0.83	2.3	57	26	3	28	2	3	0.01	4.5	171	0.01
KL32-07	504	507	0.505	5050	0.21	1.8	245	154	16	29	1	3	0.7	4.3	58	0.01
KL32-07	507	510	0.501	5010	0.19	1.5	72	49	8	32	2	3	0.7	3.4	69	0.01
KL32-07	510	513	0.325	3250	0.17	1.1	51	51	2	29	1	2	0.01	3.3	66	0.01
KL32-07	513	516	0.475	4750	0.19	1	66	56	17	33	1	0.01	1.5	5.0	51	0.01
KL32-07	516	519	0.59	5900	0.24	1.5	83	75	28	22	2	4	2.5	5.8	50	0.01
KL32-07	519	522	0.62	6200	0.14	2.2	125	76	23	31	4	4	2.2	3.8	56	0.01
KL32-07	522	525	1.14	11400	0.54	1.6	59	13	7	16	0.01	13	0.8	6.8	57	0.01
KL32-07	525	528	0.59	5900	0.24	1.2	98	75	6	62	1	4	0.8	4.5	49	0.01
KL32-07	528	531	0.54	5400	0.31	1.9	127	104	24	70	1	5	8.5	4.5	41	0.01
KL32-07	531	534	0.58	5800	0.14	1.1	75	37	6	38	0.01	4	1.2	4.3	66	0.01
KL32-07	534	537	0.59	5900	0.15	1.6	124	161	6	36	2	5	5.9	4.3	66	0.01
KL32-07	537	540	0.76	7600	0.21	1.8	209	110	11	60	3	6	11.5	5.9	131	0.01
KL32-07	540	543	0.56	5600	0.22	1.5	110	61	3	35	1	4	0.6	4.8	71	0.01
KL32-07	543	546	0.51	5100	0.2	2.4	127	62	5	81	4	6	1	6.0	56	0.01
KL32-07	546	549	0.515	5150	0.12	2.5	306	178	6	66	3	4	1.2	4.4	61	0.01
KL32-07	549	552	0.53	5300	0.09	1.8	165	115	6	35	2	3	2.4	3.5	58	0.01
KL32-07	552	555	0.369	3690	0.05	1.2	161	110	9	47	1	3	3.9	3.5	62	0.01
KL32-07	555	558	0.409	4090	0.08	1.8	313	145	13	40	2	0.01	2.2	4.0	54	0.01
KL32-07	558	561	0.425	4250	0.07	1.5	228	106	13	29	1	4	2.3	4.8	60	0.01
KL32-07	561	564	0.64	6400	0.19	1.5	227	110	7	43	0.01	5	1.4	5.8	62	0.01
KL32-07	564	567	0.88	8800	0.53	3.2	85	32	4	100	1	8	1.5	5.5	133	0.01
KL32-07	567	570	0.72	7200	0.18	1.6	132	54	5	46	0.01	8	1.9	5.0	67	0.01
KL32-07	570	573	0.52	5200	0.14	1.1	97	55	12	111	0.01	5	3.6	4.8	66	0.01
KL32-07	573	576	0.51	5100	0.11	1.8	152	75	7	37	1	7	3	5.4	61	0.01
KL32-07	576	579	0.73	7300	0.13	1.6	77	41	5	30	0.01	9	1.3	4.3	64	0.01
KL32-07	579	582	0.73	7300	0.15	1.1	60	28	2	24	0.01	8	0.2	4.3	64	0.01
KL32-07	582	585	0.59	5900	0.16	1.3	74	22	3	41	0.01	7	0.3	4.0	66	0.01
KL32-07	585	588	0.79	7900	0.22	1.9	520	218	13	29	0.01	8	3.2	4.5	49	0.01
KL32-07	588	591	0.77	7700	0.22	2.2	326	156	9	91	1	7	1.2	4.0	50	0.01
KL32-07	591	594	0.71	7100	0.18	2.4	119	67	2	51	0.01	8	0.3	3.8	57	0.01
KL32-07	594	597	0.73	7300	0.13	1.4	103	51	4	44	0.01	5	0.7	4.0	68	0.01
KL32-07	597	600	0.23	2300	0.08	0.7	68	46	0.01	17	0.01	0.01	0.01	2.3	68	0.01
KL32-07	600	603	0.359	3590	0.22	0.8	71	37	0.01	20	1	3	0.4	3.0	74	0.01
KL32-07	603	606	0.422	4220	0.18	1.1	94	63	0.01	46	1	4	0.2	3.0	68	0.01
KL32-07	606	609.5	0.412	4120	0.15	1.4	72	46	0.01	35	0.01	5	0.3	3.8	76	0.01
KL32-07	609.5	612	0.487	4870	0.1	1.5	84	45	0.01	46	0.01	7	0.5	3.5	59	0.01
KL32-07	612	615	0.485	4850	0.12	1.7	61	34	1	38	0.01	5	0.4	4.0	70	0.01
KL32-07	615	618	0.44	4400	0.09	1.4	85	44	1	53	0.01	5	1	4.5	86	0.01
KL32-07	618	621	0.366	3660	0.12	1.1	93	53	2	45	0.01	3	0.5	3.8	69	0.01
KL32-07	621	624	0.395	3950	0.09	1.7	77	116	1	36	1	6	0.5	3.5	69	0.01
KL32-07	624	627	0.42	4200	0.09	1.8	98	69	3	39	1	6	2.4	3.7	68	0.01
KL32-07	627	630	0.24	2400	0.02	1.2	48	29	5	69	0.01	4	1.8	2.8	91	0.01
KL32-07	630	633	0.4	4000	0.05	1.4	59	35	1	35	1	5	0.9	3.0	219	0.01
KL32-07	633	636	0.31	3100	0.04	1.1	121	69	7	59	1	5	1.9	3.2	146	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL32-07	636	639	0.7	7000	0.5	1	51	36	4	18	2	5	0.2	3.6	208	0.01
KL32-07	639	642	0.32	3200	0.06	0.9	114	92	7	30	0.01	4	1.3	2.0	168	0.01
KL32-07	642	645	0.25	2500	0.03	0.8	143	86	9	34	0.01	3	1.8	2.5	79	0.01
KL32-07	645	648	0.27	2700	0.04	0.6	284	142	12	40	0.01	4	1.5	2.0	75	0.01
KL32-07	648	651	0.26	2600	0.03	0.01	178	87	5	42	0.01	3	1.1	2.8	94	0.01
KL32-07	651	654	0.24	2400	0.03	0.6	104	71	8	37	0.01	3	1	1.7	180	0.01
KL32-07	654	657	0.24	2400	0.05	0.7	68	35	8	49	0.01	5	1.6	2.9	82	0.01
KL32-07	657	660	0.27	2700	0.03	0.6	66	36	15	35	0.01	5	1.2	2.8	89	0.01
KL32-07	660	663	0.28	2800	0.02	0.01	46	30	7	46	0.01	5	0.5	2.5	84	0.01
KL32-07	663	666	0.415	4150	0.06	0.9	79	34	10	25	0.01	4	1	2.0	68	0.01
KL32-07	666	669	0.225	2250	0.02	0.01	87	46	17	37	0.01	2	1.4	2.3	92	0.01
KL32-07	669	672	0.25	2500	0.01	0.5	78	40	10	53	0.01	0.01	1	2.4	99	0.01
KL32-07	672	675	0.34	3400	0.05	1.3	216	85	8	75	0.01	8	1.3	2.4	87	0.01
KL32-07	675	678	0.33	3300	0.04	1.2	357	180	7	67	0.01	5	0.8	2.8	89	0.01
KL32-07	678	681	0.22	2200	0.03	0.6	81	41	4	80	0.01	3	1.1	1.8	91	0.01
KL32-07	681	684	0.173	1730	0.03	0.7	64	41	4	87	1	2	0.8	1.5	71	0.01
KL32-07	684	687	0.23	2300	0.04	0.8	35	24	4	46	0.01	4	1.9	2.6	99	0.01
KL32-07	687	690	0.21	2100	0.05	0.7	34	18	3	52	0.01	3	0.7	2.3	84	0.01
KL32-07	690	693	0.131	1310	0.04	0.01	25	14	2	94	0.01	2	0.4	1.3	176	0.01
KL32-07	693	696	0.2	2000	0.03	0.7	77	50	20	78	0.01	5	4.6	2.3	79	0.01
KL32-07	696	699	0.24	2400	0.05	0.9	85	47	4	60	0.01	6	1.4	3.6	81	0.01
KL32-07	699	702	0.21	2100	0.02	1.3	152	78	7	102	1	2	1.3	2.8	63	0.01
KL32-07	702	705	0.23	2300	0.03	0.01	41	26	11	191	0.01	3	0.8	2.3	70	0.01
KL32-07	705	708	0.34	3400	0.03	0.7	105	67	18	210	0.01	4	2.5	3.4	73	0.01
KL32-07	708	711	0.24	2400	0.01	0.5	58	30	27	167	0.01	4	0.6	3.0	64	0.01
KL32-07	711	714	0.3	3000	0.01	0.9	129	60	7	88	0.01	5	1.3	2.7	74	0.01
KL32-07	714	717	0.27	2700	0.01	0.6	65	34	11	72	0.01	4	0.9	2.4	75	0.01
KL32-07	717	720	0.2	2000	0.02	0.01	134	30	12	43	0.01	6	0.5	1.5	87	0.01
KL32-07	720	723	0.21	2100	0.01	0.01	51	28	3	55	0.01	4	0.7	1.1	46	0.01
KL32-07	723	726	0.19	1900	0.01	0.5	45	26	7	86	0.01	0.01	0.5	2.1	45	0.01
KL32-07	726	729	0.29	2900	0.01	0.01	34	15	3	54	0.01	5	0.3	2.9	58	0.01
KL32-07	729	732	0.203	2030	0.01	0.01	36	18	6	40	0.01	4	0.4	1.3	45	0.01
KL32-07	732	735	0.25	2500	0.05	0.01	42	48	42	25	1	5	0.5	2.4	52	0.01
KL32-07	735	738	0.23	2300	0.03	0.7	54	32	9	59	1	5	0.5	1.7	50	0.01
KL32-07	738	741	0.2	2000	0.01	0.7	48	38	10	23	1	3	0.7	2.7	43	0.01
KL32-07	741	744	0.21	2100	0.01	0.01	40	26	5	27	1	4	0.5	2.6	45	0.01
KL32-07	744	747	0.21	2100	0.01	0.01	54	30	8	60	1	3	0.4	2.4	47	0.01
KL32-07	747	750	0.25	2500	0.02	0.01	43	28	4	40	0.01	5	0.4	1.8	56	0.01
KL32-07	750	753	0.21	2100	0.03	0.6	75	46	4	34	1	4	1	2.0	60	0.01
KL32-07	753	756	0.2	2000	0.03	0.7	115	68	4	53	2	5	0.8	2.9	49	0.01
KL32-07	756	759	0.197	1970	0.02	0.6	50	32	3	31	1	4	0.5	1.8	56	0.01
KL32-07	759	762	0.187	1870	0.02	0.7	73	38	5	26	1	3	0.4	1.9	39	0.01
KL32-07	762	765	0.173	1730	0.03	0.01	58	28	1	27	0.01	5	0.4	1.6	31	0.01
KL32-07	765	768	0.22	2200	0.02	0.01	33	30	22	31	0.01	4	0.4	2.0	40	0.01
KL32-07	768	771	0.2	2000	0.01	0.01	29	17	1	37	0.01	4	0.4	1.5	39	0.01
KL32-07	771	774	0.21	2100	0.01	0.7	37	24	3	74	0.01	0.01	0.6	2.5	35	0.01
KL32-07	774	777	0.152	1520	0.03	0.5	31	24	2	15	1	6	0.3	1.3	33	0.01
KL32-07	777	780	0.2	2000	0.03	0.7	38	21	0.01	20	1	6	0.4	1.8	38	0.01
KL32-07	780	783	0.22	2200	0.03	0.01	36	30	3	17	1	4	0.5	1.7	36	0.01
KL32-07	783	786	0.181	1810	0.03	0.6	43	37	25	20	1	6	0.9	1.5	30	0.01
KL32-07	786	789	0.173	1730	0.03	0.7	33	27	24	22	1	4	0.9	1.6	29	0.01
KL32-07	789	792	0.16	1600	0.03	0.6	30	21	1	18	0.01	5	0.4	1.3	34	0.01
KL32-07	792	795	0.24	2400	0.06	0.01	23	14	0.01	18	0.01	5	0.3	1.6	32	0.01
KL32-07	795	798	0.23	2300	0.08	0.01	27	14	2	13	0.01	5	0.3	1.6	35	0.01
KL32-07	798	801	0.24	2400	0.07	0.7	40	28	11	17	0.01	5	0.5	1.8	37	0.01
KL32-07	801	804	0.28	2800	0.07	0.7	39	25	2	19	0.01	5	0.5	1.7	38	0.01
KL32-07	804	807	0.179	1790	0.02	0.01	27	15	2	32	0.01	3	0.4	1.8	33	0.01
KL32-07	807	810	0.24	2400	0.05	0.8	65	20	3	25	0.01	6	0.3	2.1	43	0.01
KL32-07	810	813	0.154	1540	0.01	0.01	38	17	2	23	0.01	5	0.4	1.1	28	0.01
KL32-07	813	816	0.179	1790	0.02	0.01	64	31	3	22	0.01	4	0.4	1.5	30	0.01
KL32-07	816	819	0.23	2300	0.02	0.01	56	27	1	27	0.01	4	0.5	1.6	36	0.01
KL32-08	0	5.5	0.0168	168	0.04	0.01	234	57	12	4	0.01	2	0.7	2.0	23	0.01
KL32-08	5.5	8	0.103	1030	0.02	1	1250	225	25	8	2	8	0.8	4.7	23	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL32-08	8	11.4	0.0097		97	0.01	0.01	77	47	3	6	0.01	0.01	0.5	0.5	24	0.01
KL32-08	11.4	14.4	0.0063		63	0.01	0.01	84	41	3	4	0.01	0.01	0.5	0.6	26	0.01
KL32-08	14.4	17.4	0.0054		54	0.01	0.01	170	48	4	3	0.01	0.01	0.3	0.0	25	0.01
KL32-08	17.4	20.5	0.0138		138	0.01	0.01	363	110	5	4	0.01	0.01	0.5	0.0	27	0.01
KL32-08	20.5	23.5	0.0331		331	0.01	0.01	317	244	6	7	0.01	0.01	0.9	0.6	37	0.01
KL32-08	23.5	26.5	0.0125		125	0.01	0.01	216	196	7	5	0.01	0.01	0.4	1.3	29	0.01
KL32-08	26.5	29.5	0.0067		67	0.02	0.01	196	52	6	4	0.01	0.01	0.3	1.1	22	0.01
KL32-08	29.5	32.5	0.0097		97	0.01	0.01	98	47	5	5	0.01	0.01	0.5	0.5	24	0.01
KL32-08	32.5	35.5	0.0056		56	0.01	0.01	162	42	10	4	0.01	0.01	0.4	0.7	22	0.01
KL32-08	35.5	38.2	0.0089		89	0.01	0.01	188	84	12	5	0.01	0.01	0.4	0.0	26	0.01
KL32-08	38.2	41.3	0.0053		53	0.01	0.01	161	61	7	4	0.01	0.01	0.4	0.6	22	0.01
KL32-08	41.3	44.4	0.0063		63	0.01	0.01	130	66	8	4	0.01	0.01	0.3	0.5	17	0.01
KL32-08	44.4	47.5	0.0043		43	0.01	0.01	79	43	10	5	0.01	0.01	0.7	1.0	20	0.01
KL32-08	47.5	50.5	0.0063		63	0.01	0.01	101	45	12	8	0.01	0.01	0.6	1.2	21	0.01
KL32-08	50.5	53.5	0.0052		52	0.02	0.01	79	75	6	2	0.01	0.01	0.4	0.0	16	0.01
KL32-08	53.5	56.5	0.0041		41	0.01	0.01	111	95	11	3	0.01	0.01	0.6	0.0	15	0.01
KL32-08	56.5	61.5	0.0069		69	0.01	0.01	290	94	8	3	0.01	0.01	0.5	0.8	21	0.01
KL32-08	61.5	65.5	0.0037		37	0.01	0.8	88	67	15	4	0.01	0.01	0.7	0.7	28	0.01
KL32-08	65.5	68.5	0.0028		28	0.01	0.8	164	255	11	4	0.01	2	0.6	0.8	26	0.01
KL32-08	68.5	71.5	0.0103		103	0.01	0.01	189	296	7	5	0.01	0.01	1	0.0	18	0.01
KL32-08	71.5	74.5	0.004		40	0.05	2.5	1640	1580	30	45	3	3	1.6	3.4	19	0.01
KL32-08	74.5	77.5	0.045		450	0.08	17.5	22900	23300	68	291	4	5	19	10.8	38	0.23
KL32-08	77.5	80.5	0.0042		42	0.04	1.4	720	1120	15	18	0.01	3	1.2	4.5	28	0.01
KL32-08	80.5	83.5	0.0044		44	0.04	1.2	680	960	19	14	0.01	2	1.7	1.5	23	0.01
KL32-08	83.5	86.5	0.0047		47	0.02	1.3	388	1350	23	7	0.01	3	2.2	1.8	21	0.01
KL32-08	86.5	89.5	0.013		130	0.03	1.8	720	1300	40	26	3	0.01	2.1	3.7	37	0.01
KL32-08	89.5	92.5	0.0085		85	0.04	2.1	1050	790	36	25	7	3	1.2	3.1	33	0.01
KL32-08	92.5	95.5	0.0067		67	0.02	1.2	331	610	22	10	5	2	0.9	2.2	18	0.01
KL32-08	95.5	98	0.0207		207	0.03	3.4	2950	1300	43	39	4	2	2.6	2.1	21	0.01
KL32-08	98	101.5	0.0088		88	0.07	2.4	2510	1290	63	26	7	2	2.8	3.9	21	0.1
KL32-08	101.5	104.5	0.0078		78	0.09	2	2590	1090	45	10	8	3	1.5	2.9	17	0.01
KL32-08	104.5	107.5	0.0092		92	0.02	0.8	540	370	27	7	1	4	0.7	3.3	27	0.01
KL32-08	107.5	110.5	0.0276		276	0.02	2.5	4420	2500	68	76	6	3	4.3	4.5	26	0.01
KL32-08	110.5	113.5	0.0054		54	0.05	1.3	560	345	21	15	3	2	0.8	3.4	18	0.01
KL32-08	113.5	116.5	0.0137		137	0.14	4.9	4520	2050	68	18	19	5	3	5.2	18	0.12
KL32-08	116.5	119.5	0.0066		66	0.05	2.4	1220	480	27	53	6	7	1.2	6.0	16	0.01
KL32-08	119.5	122.5	0.0077		77	0.04	2.1	1390	820	34	38	12	4	1.5	3.7	21	0.01
KL32-08	122.5	125.5	0.0125		125	0.02	1.8	1320	670	45	39	11	7	1.4	3.7	24	0.01
KL32-08	125.5	128.4	0.0146		146	0.06	2.3	2510	1460	70	28	6	2	3.6	4.6	22	0.11
KL32-08	128.4	131.5	0.0078		78	0.03	1.2	650	258	28	16	5	3	1.1	1.9	20	0.14
KL32-08	131.5	134.5	0.0321		321	0.1	10.6	10400	3700	74	74	24	3	4.8	10.5	26	0.12
KL32-08	134.5	137.5	0.0244		244	0.09	7.5	7300	3200	37	45	16	0.01	0.9	4.6	15	0.11
KL32-08	137.5	140.5	0.0293		293	0.03	4.9	2500	1450	48	38	8	2	1.5	2.8	26	0.1
KL32-08	140.5	143.5	0.047		470	0.04	6.7	6900	2700	53	551	14	4	2.2	5.7	32	0.01
KL32-08	143.5	146.5	0.058		580	0.02	3.8	4940	3020	74	104	7	3	2.6	3.8	23	0.01
KL32-08	146.5	149.5	0.056		560	0.05	6	6540	2330	60	78	16	2	1.7	4.3	20	0.1
KL32-08	149.5	152.5	0.078		780	0.05	4.9	8000	3000	42	70	22	2	1.7	10.5	26	0.12
KL32-08	152.5	155.5	0.0272		272	0.04	2.4	4630	2800	30	34	8	3	1.2	6.9	26	0.1
KL32-08	155.5	158.5	0.129		1290	0.07	7.6	12900	1770	44	158	43	5	5.3	20.5	37	0.18
KL32-08	158.5	161.5	0.0198		198	0.02	2.9	3210	1710	27	46	12	2	1.1	5.9	25	0.01
KL32-08	161.5	164.5	0.0117		117	0.02	1.5	1450	530	19	50	20	2	1.3	6.2	22	0.01
KL32-08	164.5	167.5	0.079		790	0.03	1.3	2260	440	23	21	11	11	1.4	7.5	22	0.01
KL32-08	167.5	170.5	1.03		10300	0.13	4	560	246	36	77	7	35	2	19.0	86	0.01
KL32-08	170.5	173.5	0.452		4520	0.1	0.9	235	149	14	43	4	18	0.8	4.4	84	0.01
KL32-08	173.5	176.5	0.266		2660	0.05	0.7	163	241	8	36	3	9	0.4	4.6	84	0.01
KL32-08	176.5	179.5	0.307		3070	0.09	1.1	186	129	22	22	5	10	0.8	6.9	52	0.01
KL32-08	179.5	182.5	0.23		2300	0.05	0.9	129	89	11	540	4	7	1.2	6.8	99	0.01
KL32-08	182.5	185.5	0.152		1520	0.04	0.5	58	54	7	337	2	9	0.3	3.5	129	0.01
KL32-08	185.5	188.5	1.39		13900	0.2	4.1	104	317	14	154	2	8	1	17.0	115	0.01
KL32-08	188.5	191.5	0.61		6100	0.19	4.4	131	279	48	134	17	6	0.9	9.5	59	0.01
KL32-08	191.5	194.5	0.3		3000	0.14	2.7	52	125	16	164	6	7	0.7	5.4	49	0.01
KL32-08	194.5	197.5	0.182		1820	0.03	1.5	54	80	11	133	1	7	0.9	4.7	48	0.01
KL32-08	197.5	200	0.28		2800	0.07	3.4	92	96	15	87	18	6	1	3.2	37	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL32-08	200	203	0.426	4260	0.1	6.2	760	340	37	422	5	11	0.8	6.6	101	0.01
KL32-08	203	206	0.498	4980	0.29	5.5	520	259	47	110	6	16	4	7.4	96	0.01
KL32-08	206	209	0.208	2080	0.65	11.8	7700	3700	490	100	2	6	102	10.5	157	0.32
KL32-08	209	212.5	0.145	1450	0.06	1.8	470	147	21	79	3	7	2.4	5.1	96	0.01
KL32-08	212.5	215.5	0.148	1480	0.04	5	1120	870	23	99	4	8	2.1	8.5	115	0.01
KL32-08	215.5	218.5	0.21	2100	0.06	5.6	87	352	7	110	2	12	0.6	5.7	78	0.01
KL32-08	218.5	221.5	0.339	3390	0.14	8.7	109	197	19	78	3	9	1.8	2.9	48	0.01
KL32-08	221.5	224.5	0.096	960	0.07	5.5	66	144	12	131	36	11	1.1	2.4	30	0.01
KL32-08	224.5	226.3	0.29	2900	0.12	6.4	131	155	20	426	2	12	1.4	2.6	45	0.01
KL32-08	226.3	228.5	0.23	2300	0.13	11.8	460	1390	62	107	5	7	3.1	3.5	34	0.01
KL32-08	228.5	230.5	0.15	1500	0.17	11.2	1620	1080	110	136	38	6	2	3.8	34	0.01
KL32-08	230.5	233.5	0.065	650	0.08	2	318	234	37	420	3	15	1.4	3.3	30	0.01
KL32-08	233.5	236.5	0.88	8800	0.51	50	15400	5700	340	750	275	39	82	23.5	59	0.23
KL32-08	236.5	239.5	0.34	3400	0.16	13.5	23200	9100	47	47	24	8	7.5	24.0	23	0.17
KL32-08	239.5	242.5	0.44	4400	0.43	12.1	7200	2400	110	73	16	2	5.3	8.2	20	0.14
KL32-08	242.5	245.5	0.446	4460	0.28	6.8	4830	650	100	17	14	3	6.6	4.2	25	0.15
KL32-08	245.5	248.5	0.24	2400	0.11	7.2	3440	1010	36	46	18	0.01	1.8	3.4	21	0.1
KL32-08	248.5	251.5	0.274	2740	0.09	10.5	3460	2130	29	95	32	2	2.9	3.4	23	0.1
KL32-08	251.5	253.6	0.106	1060	0.04	2.2	3440	295	10	19	4	0.01	0.7	2.9	25	0.01
KL32-08	253.6	256.8	0.151	1510	0.04	7	5600	1540	38	57	126	10	3.5	7.4	23	0.1
KL32-08	256.8	259.9	0.83	8300	0.21	9	2900	1010	190	184	15	27	19.2	11.2	28	0.11
KL32-08	259.9	263	0.62	6200	0.25	9.4	5400	1370	140	139	24	15	5.2	8.8	33	0.13
KL32-08	263	265.8	0.208	2080	0.27	3.9	4070	1030	26	18	4	3	1.2	2.9	23	0.1
KL32-08	265.8	268.8	0.61	6100	0.13	4.2	1990	580	51	39	3	9	2.1	6.4	25	0.01
KL32-08	268.8	271.5	0.0241	241	0.02	0.6	365	56	9	5	2	0.01	0.3	0.9	11	0.01
KL32-08	271.5	274.6	0.07	700	0.07	1.1	4900	470	22	17	7	0.01	0.6	3.6	14	0.01
KL32-08	274.6	277.6	0.116	1160	0.06	1.4	3460	47	14	10	0.01	4	0.2	3.0	14	0.01
KL32-08	277.6	280	0.083	830	0.1	0.9	2750	309	19	22	1	6	0.3	1.8	18	0.01
KL32-08	280	283.1	3.2	32000	3.36	18.7	1430	132	27	34	2	84	0.4	8.0	34	0.01
KL32-08	283.1	286.5	0.408	4080	0.31	3	388	176	22	418	1	13	1.2	1.9	32	0.01
KL32-08	286.5	289.6	1.01	10100	1.05	15.2	2900	206	21	16	4	41	0.8	11.5	38	0.01
KL32-08	289.6	293.5	0.145	1450	0.17	1.1	570	58	7	4	1	7	0.01	2.5	27	0.01
KL32-08	293.5	297.5	0.235	2350	0.27	2.1	4960	80	9	4	6	8	0.3	7.0	24	0.01
KL32-08	297.5	299.5	0.118	1180	0.07	1.3	1180	103	14	19	3	6	0.01	3.5	20	0.01
KL32-08	299.5	302.5	0.0263	263	0.02	0.7	2020	118	10	5	1	5	2.2	2.5	12	0.01
KL32-08	302.5	305.5	0.78	7800	0.85	5.6	2260	140	12	7	1	20	0.5	10.4	20	0.01
KL32-08	305.5	308.5	0.8	8000	0.68	2.9	30100	65	9	20	1	150	1	20.5	26	0.01
KL32-08	308.5	311.5	0.83	8300	0.78	3.2	33700	60	19	41	1	175	2	23.0	25	0.01
KL32-08	311.5	314	0.36	3600	0.45	2.7	13500	170	21	16	4	46	1.7	9.8	32	0.01
KL32-08	314	317	0.45	4500	0.58	2.6	14000	24	23	56	5	90	12.1	9.0	26	0.01
KL32-08	317	320.2	0.73	7300	0.04	2	4500	28	35	16	4	31	1.4	12.0	29	0.01
KL32-08	320.2	323.3	0.91	9100	0.88	1.6	820	27	14	300	1	50	0.8	20.5	26	0.01
KL32-08	323.3	326.4	0.65	6500	0.66	2.1	399	42	11	87	0.01	23	0.5	9.5	23	0.01
KL32-08	326.4	329.5	1.2	12000	0.87	3.5	460	44	16	118	0.01	52	0.01	6.3	29	0.01
KL32-08	329.5	332.5	0.32	3200	0.24	1.8	355	34	15	356	0.01	23	0.01	4.3	20	0.01
KL32-08	332.5	335.5	0.151	1510	0.14	1.3	242	78	18	53	0.01	13	0.7	3.5	21	0.01
KL32-08	335.5	338.5	0.197	1970	0.15	1.2	174	37	5	24	0.01	10	0.7	4.3	9	0.01
KL32-08	338.5	341.8	0.409	4090	0.25	1.7	88	49	3	63	0.01	16	0.4	7.3	14	0.01
KL32-08	341.8	344.5	0.76	7600	0.32	1.8	156	21	16	247	0.01	19	0.01	4.8	15	0.01
KL32-08	344.5	347.5	0.7	7000	0.25	2.3	490	83	18	33	1	24	3.6	6.5	22	0.01
KL32-08	347.5	350.5	0.9	9000	0.37	4.6	430	39	22	120	0.01	48	1.1	6.3	24	0.01
KL32-08	350.5	353.5	0.93	9300	0.44	5.2	700	41	11	31	0.01	32	0.5	6.5	10	0.01
KL32-08	353.5	356.5	2.85	28500	2.04	17.1	1120	28	4	120	0.01	82	0.01	16.0	17	0.01
KL32-08	356.5	359.5	2.43	24300	0.76	6.7	1040	21	9	32	1	45	0.3	13.0	15	0.01
KL32-08	359.5	362.5	5.14	51400	1.2	12.4	800	16	5	18	1	62	0.4	21.2	11	0.01
KL32-08	362.5	365.5	1.83	18300	0.51	4.7	560	19	10	10	0.01	40	0.3	11.0	17	0.01
KL32-08	365.5	368.5	0.62	6200	0.29	2.5	7500	20	28	23	3	38	3.4	5.0	14	0.01
KL32-08	368.5	371.5	0.58	5800	0.38	3.9	5700	19	23	16	4	46	1.3	9.3	12	0.01
KL32-08	371.5	374.5	0.422	4220	0.13	3.4	276	37	20	15	1	19	0.8	5.5	8	0.01
KL32-08	374.5	377.5	0.22	2200	0.18	1.6	570	46	7	125	4	13	0.4	5.0	14	0.01
KL32-08	377.5	380.5	0.69	6900	0.48	5.8	4170	97	20	16	5	49	6.7	12.3	16	0.01
KL32-08	380.5	383.5	0.65	6500	0.54	6.5	4470	19	18	10	7	31	0.3	34.5	14	0.01
KL32-08	383.5	386.5	0.27	2700	0.32	1.8	980	21	10	8	6	49	0.9	10.5	19	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL32-08	386.5	389.5	0.425	4250	0.27	2.4	1920	30	17	11	2	34	2.8	8.5	17	0.01
KL32-08	389.5	392.5	0.33	3300	0.12	0.7	265	12	0.01	41	0.01	31	0.01	2.8	9	0.01
KL32-08	392.5	395.5	0.449	4490	0.3	2.2	410	23	28	14	5	16	0.8	30.5	18	0.01
KL32-08	395.5	398.5	1.1	11000	0.38	3.1	254	28	9	116	0.01	46	2.1	9.0	19	0.01
KL32-08	398.5	401.5	0.77	7700	0.47	1.7	159	36	5	14	0.01	38	0.2	7.5	16	0.01
KL32-08	401.5	404.5	0.69	6900	0.26	1.2	143	17	3	9	0.01	23	4.7	4.8	13	0.01
KL32-08	404.5	407.5	0.52	5200	0.37	2.9	17500	69	18	29	2	77	1.4	33.0	15	0.01
KL32-08	407.5	410.5	0.509	5090	0.17	1.5	87	17	4	31	0.01	28	0.01	5.0	6	0.01
KL32-08	410.5	413.5	1	10000	0.37	1.9	131	18	7	33	0.01	42	0.01	6.5	32	0.01
KL32-08	413.5	416.5	0.338	3380	0.15	0.6	121	12	0.01	8	2	47	0.01	2.3	24	0.01
KL32-08	416.5	419.5	0.485	4850	0.2	0.6	112	11	0.01	22	0.01	45	0.01	3.5	19	0.01
KL32-08	419.5	422.5	0.17	1700	0.12	0.5	147	13	0.01	6	0.01	41	0.01	1.5	13	0.01
KL32-08	422.5	425.3	0.26	2600	0.12	0.01	71	11	1	9	0.01	18	0.01	3.3	25	0.01
KL32-08	425.3	428.4	0.76	7600	0.34	0.8	126	25	1	36	0.01	32	0.01	4.3	31	0.01
KL32-08	428.4	431.5	3.06	30600	1.25	3.5	157	19	0.01	6	0.01	42	0.01	17.0	32	0.01
KL32-08	431.5	434.5	1.54	15400	0.78	2	188	19	1	175	0.01	43	0.01	8.0	23	0.01
KL32-08	434.5	437.6	1.06	10600	0.5	1.9	125	27	3	41	0.01	20	0.01	6.6	30	0.01
KL32-08	437.6	441.1	1.68	16800	1.2	2.7	72	14	0.01	6	0.01	34	0.01	11.0	25	0.01
KL32-08	441.1	443.5	1.12	11200	0.41	7	241	68	230	59	1	35	23	8.5	47	0.01
KL32-08	443.5	446.5	0.512	5120	0.32	7.6	313	122	240	159	4	73	78	12.8	70	0.01
KL32-08	446.5	449.5	0.64	6400	0.25	1.1	99	22	8	50	3	6	1.3	5.3	45	0.01
KL32-08	449.5	452.5	1.5	15000	0.74	4.4	116	107	12	31	23	18	0.8	20.0	50	0.01
KL32-08	452.5	455.5	0.82	8200	0.54	4.3	47	23	6	22	4	17	1.4	6.0	47	0.01
KL32-08	455.5	458.5	0.66	6600	0.6	8.2	272	1110	270	10	3	108	20	55.8	73	0.12
KL32-08	458.5	461.5	0.153	1530	0.5	4.2	1650	1590	220	5	2	104	12.3	21.4	95	0.1
KL32-08	461.5	464.5	0.26	2600	0.19	0.9	273	346	12	36	1	29	1.3	7.5	35	0.01
KL32-08	464.5	467.4	0.6	6000	0.31	1.3	59	21	1	70	1	9	0.01	4.0	51	0.01
KL32-08	467.4	470.5	0.506	5060	0.43	0.9	45	17	1	25	1	5	0.01	4.5	58	0.01
KL32-08	470.5	473.5	0.69	6900	0.53	1.1	42	15	1	110	1	4	0.01	4.3	60	0.01
KL32-08	473.5	476.5	0.72	7200	0.43	1.2	41	17	3	34	1	8	0.01	4.5	106	0.01
KL32-08	476.5	479.5	0.392	3920	0.26	0.7	31	11	1	31	1	6	0.01	3.9	70	0.01
KL32-08	479.5	482.5	0.361	3610	0.28	0.8	44	13	1	36	2	8	0.01	3.0	62	0.01
KL32-08	482.5	485.5	0.449	4490	0.2	1.2	89	23	1	34	2	7	0.01	4.8	58	0.01
KL32-08	485.5	488.5	0.464	4640	0.25	1.1	56	24	2	25	2	8	0.01	3.8	77	0.01
KL32-08	488.5	491.5	0.475	4750	0.43	0.7	52	19	1	16	0.01	6	0.01	3.3	76	0.01
KL32-08	491.5	494.5	0.56	5600	0.4	1	68	18	1	19	1	9	0.01	3.3	80	0.01
KL32-08	494.5	497.5	0.463	4630	0.31	0.5	64	14	1	20	1	8	0.01	3.3	87	0.11
KL32-08	497.5	500.5	0.8	8000	0.39	1.1	50	22	60	31	1	10	2.3	5.5	72	0.01
KL32-08	500.5	503.5	0.33	3300	0.19	0.6	25	10	0.01	16	0.01	5	0.01	3.0	85	0.01
KL32-08	503.5	506.5	0.387	3870	0.28	0.8	25	14	1	17	2	4	0.01	3.5	66	0.01
KL32-08	506.5	509.5	0.37	3700	0.19	0.5	40	11	3	12	1	6	0.01	2.8	70	0.01
KL32-08	509.5	512.5	0.489	4890	0.29	0.9	50	11	0.01	66	1	10	0.01	3.0	65	0.01
KL32-08	512.5	515.5	0.56	5600	0.26	2.1	82	43	1	20	2	7	0.6	4.5	99	0.01
KL32-08	515.5	518.5	0.73	7300	0.35	1.6	52	16	2	27	0.01	15	0.4	4.0	82	0.01
KL32-08	518.5	521.5	0.392	3920	0.21	2	83	30	1	16	1	9	0.01	2.5	79	0.01
KL32-08	521.5	524.5	0.34	3400	0.21	0.8	47	14	1	24	0.01	6	0.01	2.5	86	0.01
KL32-08	524.5	527.5	0.462	4620	0.27	1.1	52	17	1	35	1	8	0.01	4.7	99	0.01
KL32-08	527.5	530.5	0.468	4680	0.49	0.9	38	11	0.01	12	0.01	5	0.01	4.0	82	0.01
KL32-08	530.5	533.5	0.26	2600	0.23	0.6	49	9	0.01	42	0.01	3	0.01	2.0	78	0.01
KL32-08	533.5	536.5	0.483	4830	0.31	1.3	58	15	1	21	2	10	0.01	3.9	77	0.01
KL32-08	536.5	539.5	0.496	4960	0.35	1.3	105	14	1	43	0.01	11	0.01	4.8	76	0.01
KL32-08	539.5	542.5	0.69	6900	0.34	2.1	980	80	1	15	3	14	0.01	4.5	97	0.01
KL32-08	542.5	545.5	0.486	4860	0.47	1	74	15	0.01	31	0.01	10	0.01	4.5	73	0.01
KL32-08	545.5	548.5	0.348	3480	0.5	1.4	90	21	1	19	5	11	0.8	17.5	87	0.01
KL32-08	548.5	551.5	0.367	3670	0.25	1.3	57	13	2	34	0.01	7	0.2	4.0	68	0.01
KL32-08	551.5	554.4	0.415	4150	0.35	1.1	49	13	0.01	16	1	8	0.01	3.8	71	0.01
KL32-08	554.4	557.5	0.381	3810	0.32	1	44	7	0.01	13	0.01	8	0.01	4.3	69	0.01
KL32-08	557.5	561.7	0.74	7400	0.71	1.5	53	9	0.01	17	1	9	0.01	7.4	74	0.01
KL32-08	561.7	563.5	0.58	5800	0.5	1.1	53	9	1	19	1	9	0.01	3.8	79	0.01
KL32-08	563.5	566.5	1.1	11000	1.07	1.9	64	10	1	6	3	8	0.01	4.5	65	0.01
KL32-08	566.5	568.4	0.84	8400	0.31	1.8	67	7	1	105	0.01	11	0.01	4.0	64	0.01
KL32-08	568.4	571	0.3	3000	0.24	1	35	13	1	27	0.01	5	0.2	2.7	56	0.01
KL32-08	571	573.2	0.393	3930	0.35	1.1	53	16	1	12	0.01	3	0.01	2.0	32	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL32-08	573.2	575.4	0.61	6100	0.51	1.1	45	27	3	7	0.01	9	0.01	3.0	45	0.01
KL32-08	575.4	578.5	0.51	5100	0.43	1.1	44	13	0.01	16	0.01	8	0.01	3.1	60	0.01
KL32-08	578.5	582	0.74	7400	0.26	1.6	52	16	1	16	0.01	8	0.01	3.6	47	0.01
KL32-08	582	584.5	0.342	3420	0.13	2.1	570	218	170	19	3	11	1.6	5.4	108	0.01
KL32-08	584.5	587.5	0.207	2070	0.02	1.2	176	60	62	23	2	3	1	1.7	151	0.01
KL32-08	587.5	590.5	0.105	1050	0.03	1	320	110	140	15	1	3	0.6	3.6	150	0.01
KL32-08	590.5	593.5	0.171	1710	0.04	0.8	301	96	32	22	1	0.01	0.5	1.7	193	0.01
KL32-08	593.5	596.4	0.23	2300	0.02	0.7	225	80	9	52	1	0.01	0.6	2.0	168	0.01
KL32-08	596.4	599.5	0.28	2800	0.04	0.8	263	408	43	42	0.01	0.01	2.8	2.1	190	0.01
KL32-08	599.5	602.5	0.152	1520	0.01	0.5	127	48	22	25	0.01	0.01	0.4	1.7	173	0.01
KL32-08	602.5	605.5	0.32	3200	0.04	0.9	83	32	0.01	17	1	0.01	0.5	2.6	196	0.01
KL32-08	605.5	608.5	0.493	4930	0.13	1.1	104	21	0.01	17	1	2	0.01	4.0	133	0.01
KL32-08	608.5	611.5	0.6	6000	0.12	1.2	355	104	61	14	1	2	0.5	3.2	144	0.01
KL32-08	611.5	614.5	0.448	4480	0.06	1.1	39	14	2	13	1	2	0.3	2.6	160	0.01
KL32-08	614.5	617.5	0.504	5040	0.1	1.3	25	10	34	12	1	3	0.2	3.0	179	0.01
KL32-08	617.5	620.5	0.61	6100	0.04	1.2	30	12	24	14	0.01	0.01	0.2	2.8	165	0.01
KL32-08	620.5	623.5	0.29	2900	0.03	1	44	20	240	26	0.01	3	3.1	2.3	211	0.01
KL32-08	623.5	626.5	0.392	3920	0.02	0.7	41	21	0.01	36	0.01	3	0.2	1.8	177	0.01
KL32-08	626.5	629.5	0.21	2100	0.02	1	317	67	24	32	1	3	0.3	1.7	270	0.01
KL32-08	629.5	632.5	0.21	2100	0.01	0.7	237	78	19	25	1	6	0.5	3.1	213	0.01
KL32-08	632.5	635.5	0.23	2300	0.01	0.9	630	215	11	27	1	3	0.4	2.0	209	0.01
KL32-08	635.5	638.5	0.105	1050	0.01	0.01	187	63	8	37	0.01	5	0.4	2.5	285	0.01
KL32-08	638.5	641.5	0.082	820	0.01	0.01	80	25	6	17	0.01	2	0.4	1.4	190	0.01
KL32-08	641.5	644.5	0.0277	277	0.01	0.01	43	15	6	15	0.01	4	0.4	2.4	343	0.01
KL32-08	644.5	647.5	0.52	5200	0.04	1.3	20	8	4	15	2	3	1	2.4	211	0.01
KL32-08	647.5	650.5	0.162	1620	0.02	0.5	22	8	1	23	0.01	2	0.5	1.6	201	0.01
KL32-08	650.5	653.5	0.24	2400	0.03	0.6	135	50	9	22	2	6	0.3	3.4	318	0.01
KL32-08	653.5	656.5	0.021	210	0.01	0.7	305	220	25	24	1	8	0.4	4.8	120	0.01
KL32-08	656.5	659.5	0.052	520	0.02	0.01	141	37	13	19	4	4	0.5	3.2	207	0.01
KL32-08	659.5	662.5	0.29	2900	0.04	0.01	30	12	4	18	1	4	0.5	3.7	170	0.01
KL32-08	662.5	665.5	0.404	4040	0.02	0.7	99	27	2	17	1	4	0.6	2.1	137	0.01
KL32-08	665.5	668.5	0.32	3200	0.01	1.4	421	160	30	31	1	2	0.4	1.4	197	0.01
KL32-08	668.5	671.5	0.21	2100	0.02	0.7	101	28	0.01	28	0.01	2	0.3	1.8	207	0.01
KL32-08	671.5	674.5	0.171	1710	0.01	0.01	54	15	1	23	0.01	2	0.2	1.2	255	0.01
KL32-08	674.5	677.5	0.104	1040	0.01	0.01	90	28	7	55	0.01	3	0.2	1.1	333	0.01
KL32-08	677.5	680.5	0.014	140	0.01	0.01	145	53	19	28	0.01	2	0.3	1.0	216	0.01
KL32-08	680.5	683.1	0.068	680	0.02	0.7	145	76	76	17	0.01	2	0.8	0.8	337	0.01
KL32-08	683.1	686.5	0.0401	401	0.01	0.7	168	114	63	21	0.01	2	2.3	0.8	290	0.01
KL32-08	686.5	689.5	0.093	930	0.01	0.5	130	60	77	19	0.01	0.01	0.7	1.4	294	0.01
KL32-08	689.5	692	0.161	1610	0.03	1.1	195	242	280	25	1	2	2.7	2.6	230	0.12
KL32-08	692	695.1	0.09	900	0.01	0.01	69	52	45	22	0.01	3	0.4	1.6	266	0.01
KL32-08	695.1	698.2	0.083	830	0.02	0.5	202	65	40	22	0.01	3	0.4	2.3	265	0.01
KL32-08	698.2	701.5	0.109	1090	0.03	0.01	68	26	1	17	0.01	0.01	0.2	1.8	192	0.01
KL32-08	701.5	704.5	0.101	1010	0.02	0.01	139	46	15	26	0.01	0.01	0.3	1.9	208	0.01
KL32-08	704.5	707.5	0.09	900	0.01	0.01	168	89	97	19	1	3	1.3	2.5	348	0.01
KL32-08	707.5	710.5	0.132	1320	0.02	0.01	23	15	64	28	0.01	0.01	0.5	1.7	217	0.01
KL32-08	710.5	713.5	0.171	1710	0.04	0.01	27	10	2	24	0.01	2	0.2	1.8	300	0.01
KL32-08	713.5	716.5	0.259	2590	0.03	0.6	59	18	3	23	0.01	2	0.3	2.4	206	0.01
KL32-08	716.5	719.5	0.197	1970	0.03	0.5	78	25	1	23	0.01	0.01	0.2	2.2	222	0.01
KL32-08	719.5	722.5	0.179	1790	0.04	0.5	217	62	3	40	0.01	0.01	0.2	2.5	289	0.01
KL32-08	722.5	725.4	0.156	1560	0.03	0.01	33	17	30	26	1	0.01	0.3	2.3	194	0.01
KL32-08	725.4	728.5	0.18	1800	0.02	0.01	110	36	9	83	0.01	0.01	0.2	1.9	244	0.01
KL32-08	728.5	731.5	0.135	1350	0.2	0.6	134	27	4	33	0.01	0.01	0.3	2.0	340	0.01
KL32-08	731.5	734.5	0.176	1760	0.05	0.01	34	16	1	24	0.01	0.01	0.2	2.2	307	0.01
KL32-08	734.5	737.5	0.09	900	0.03	0.01	245	119	41	31	1	0.01	0.5	3.2	251	0.01
KL32-08	737.5	740.5	0.166	1660	0.03	0.6	66	36	68	20	0.01	2	1.3	1.9	339	0.01
KL32-08	740.5	743.5	0.1	1000	0.03	0.01	314	74	11	48	0.01	5	0.6	3.4	194	0.01
KL32-08	743.5	746.5	0.06	600	0.06	0.01	132	116	63	42	1	2	3.8	3.4	386	0.01
KL32-08	746.5	749.5	0.154	1540	0.05	0.01	50	66	310	25	3	3	4.4	4.7	250	0.01
KL32-08	749.5	752.5	0.117	1170	0.02	0.01	218	95	370	19	1	0.01	1.9	2.7	338	0.01
KL32-08	752.5	755.5	0.216	2160	0.04	1.1	175	46	460	24	1	20	6.4	6.6	158	0.01
KL32-08	755.5	758.5	0.26	2600	0.04	0.7	158	55	14	16	2	5	0.6	3.3	193	0.01
KL32-08	758.5	761.5	0.206	2060	0.04	2.1	346	179	50	19	4	7	3.1	8.0	161	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL32-08	761.5	764.5	0.382		3820	0.04	1.1	142	54	11	17	3	2	0.3	1.7	141	0.01
KL32-08	764.5	767.5	0.177		1770	0.03	1	113	47	120	17	4	2	4.3	2.6	186	0.01
KL32-08	767.5	770.5	0.29		2900	0.02	0.8	81	41	180	18	1	3	1.4	1.8	123	0.01
KL32-08	770.5	773.5	0.124		1240	0.04	0.5	218	128	38	24	1	0.01	0.3	2.5	187	0.01
KL32-08	773.5	776.1	0.434		4340	0.02	1.1	262	98	2	17	0.01	2	0.01	2.3	169	0.01
KL32-08	776.1	779.5	0.26		2600	0.03	0.7	121	45	7	21	1	4	0.4	2.1	110	0.01
KL32-08	779.5	782.3	0.088		880	0.03	0.01	189	56	6	47	1	2	0.7	2.4	155	0.01
KL32-08	782.3	785.5	0.155		1550	0.02	0.01	47	9	1	27	0.01	0.01	0.2	2.9	290	0.01
KL32-08	785.5	788.5	0.21		2100	0.04	0.01	49	13	2	20	0.01	3	0.3	2.2	222	0.01
KL32-08	788.5	791.6	0.2		2000	0.02	0.01	52	13	1	39	0.01	2	0.2	1.7	162	0.01
KL32-08	791.6	794.5	0.23		2300	0.03	0.01	59	28	0.01	36	0.01	0.01	0.2	3.2	198	0.01
KL32-08	794.5	797.5	0.23		2300	0.03	0.01	51	17	0.01	31	0.01	2	0.01	1.3	136	0.01
KL32-08	797.5	800.5	0.195		1950	0.1	0.01	38	12	1	42	0.01	3	0.01	1.2	144	0.01
KL32-08	800.5	803.5	0.123		1230	0.06	0.01	16	0.01	2	22	0.01	2	0.3	0.9	156	0.01
KL32-08	803.5	806.5	0.157		1570	0.12	0.01	21	0.01	1	45	0.01	3	0.2	1.6	212	0.01
KL32-08	806.5	809.8	0.156		1560	0.02	0.01	47	10	1	34	0.01	3	0.2	1.8	231	0.01
KL32-08	809.8	812.5	0.171		1710	0.02	0.01	570	153	9	38	0.01	2	0.3	2.3	243	0.01
KL32-08	812.5	815.5	0.39		3900	0.06	2	296	142	57	51	3	0.01	1.2	4.0	171	0.01
KL32-08	815.5	818.5	0.172		1720	0.04	0.9	79	27	69	71	11	2	9.4	2.8	267	0.01
KL32-08	818.5	821.5	0.162		1620	0.03	0.8	68	22	56	17	0.01	0.01	0.4	0.8	150	0.01
KL32-08	821.5	824.5	0.084		840	0.01	0.01	96	44	190	12	0.01	3	1	2.6	210	0.01
KL32-08	824.5	827.5	0.109		1090	0.01	0.01	89	30	5	8	0.01	3	0.2	1.8	224	0.01
KL32-08	827.5	830.5	0.113		1130	0.02	0.01	54	18	2	23	0.01	2	0.4	1.6	264	0.01
KL32-08	830.5	833.5	0.097		970	0.01	0.01	42	13	1	26	0.01	0.01	0.2	0.9	165	0.01
KL32-08	833.5	836.5	0.136		1360	0.03	0.01	56	18	2	64	0.01	0.01	0.01	1.1	155	0.01
KL32-08	836.5	839.5	0.192		1920	0.05	0.01	95	35	130	19	3	0.01	9.1	3.5	237	0.01
KL32-08	839.5	842.5	0.162		1620	0.06	0.01	42	17	20	20	0.01	2	0.4	2.4	194	0.01
KL32-08	842.5	845.5	0.159		1590	0.03	0.01	54	26	20	19	0.01	2	0.4	1.8	163	0.01
KL32-08	845.5	848.5	0.149		1490	0.02	0.01	27	10	5	28	0.01	3	0.3	2.3	110	0.01
KL32-08	848.5	851.5	0.116		1160	0.01	0.01	19	8	1	19	0.01	0.01	0.2	1.3	147	0.01
KL32-08	851.5	854.5	0.162		1620	0.01	0.01	17	6	1	20	0.01	0.01	0.2	0.7	155	0.01
KL32-08	854.5	857.5	0.149		1490	0.08	0.01	30	10	1	22	0.01	2	0.01	0.8	237	0.01
KL32-08	857.5	860.5	0.104		1040	0.02	0.01	16	8	1	34	0.01	2	0.01	1.6	205	0.01
KL32-08	860.5	863.5	0.181		1810	0.03	0.01	65	33	6	21	0.01	2	0.01	2.7	212	0.01
KL32-08	863.5	866.5	0.121		1210	0.03	0.01	23	7	1	39	0.01	3	0.01	2.0	251	0.01
KL32-08	866.5	869.5	0.115		1150	0.06	0.01	77	26	31	40	1	6	3.1	4.7	316	0.01
KL32-08	869.5	872.5	0.0378		378	0.02	0.01	26	21	87	34	4	4	6.9	2.7	224	0.01
KL32-08	872.5	875.5	0.29		2900	0.02	0.8	41	18	58	41	1	2	0.5	1.7	224	0.01
KL32-08	875.5	878.5	0.24		2400	0.02	0.01	100	165	50	37	0.01	0.01	0.2	1.5	132	0.01
KL32-08	878.5	880.7	0.158		1580	0.03	0.01	44	22	140	42	0.01	0.01	0.5	1.6	334	0.01
KL32-08	880.7	883.8	0.155		1550	0.01	0.01	121	42	6	21	0.01	2	0.2	1.1	168	0.01
KL32-08	883.8	886.9	0.21		2100	0.04	0.01	65	18	4	43	0.01	3	0.2	1.4	139	0.01
KL32-08	886.9	890	0.171		1710	0.04	0.01	19	0.01	0.01	74	0.01	3	0.01	1.3	183	0.01
KL32-08	890	893.5	0.105		1050	0.02	0.01	20	0.01	0.01	42	0.01	2	0.01	0.8	256	0.01
KL32-08	893.5	896.5	0.088		880	0.01	0.01	56	8	1	47	0.01	2	0.2	1.2	396	0.01
KL32-08	896.5	899.5	0.143		1430	0.05	0.01	51	14	0.01	46	0.01	0.01	0.2	0.8	198	0.01
KL32-08	899.5	902.5	0.107		1070	0.02	0.01	19	7	4	52	0.01	2	0.2	0.6	273	0.01
KL32-08	902.5	905.5	0.18		1800	0.01	0.6	20	18	59	48	0.01	3	0.01	1.1	154	0.01
KL32-08	905.5	908.5	0.26		2600	0.02	0.8	98	21	11	45	0.01	3	0.01	1.4	200	0.01
KL32-08	908.5	911.5	0.24		2400	0.03	0.8	69	14	0.01	30	0.01	4	0.2	2.4	313	0.01
KL32-08	911.5	914.5	0.27		2700	0.02	0.8	54	16	0.01	17	0.01	4	0.2	1.9	247	0.01
KL32-08	914.5	917.5	0.129		1290	0.01	0.01	184	26	2	24	0.01	2	0.3	2.4	181	0.01
KL32-08	917.5	920.5	0.22		2200	0.04	0.6	35	7	1	24	0.01	4	0.01	1.2	163	0.01
KL32-08	920.5	923.5	0.2		2000	0.06	0.01	24	7	2	21	0.01	4	0.2	1.1	190	0.01
KL32-08	923.5	926.5	0.23		2300	0.05	0.01	29	9	66	36	0.01	5	0.01	1.2	159	0.01
KL32-08	926.5	929.5	0.24		2400	0.06	0.01	23	9	44	27	0.01	4	0.01	1.7	156	0.01
KL32-08	929.5	932.5	0.27		2700	0.07	0.01	26	6	16	29	0.01	4	0.01	1.6	206	0.01
KL32-08	932.5	935.5	0.24		2400	0.08	0.01	32	6	1	26	0.01	3	0.01	1.2	178	0.01
KL32-08	935.5	938.5	0.184		1840	0.05	0.01	36	6	1	16	0.01	5	0.01	0.9	173	0.01
KL32-08	938.5	941.5	0.21		2100	0.08	0.6	146	52	4	28	0.01	4	0.01	1.4	167	0.01
KL32-08	941.5	944.5	0.24		2400	0.04	0.5	63	22	2	18	0.01	5	0.01	1.2	172	0.01
KL32-08	944.5	947.5	0.32		3200	0.04	0.7	36	12	42	16	0.01	5	0.2	1.9	162	0.01
KL32-08	947.5	950.5	0.305		3050	0.05	0.8	75	21	36	23	0.01	4	0.01	1.6	134	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL32-08	950.5	953.5	0.35		3500	0.03	0.7	67	18	5	10	0.01	5	0.01	1.3	164	0.01
KL32-08	953.5	956.5	0.164		1640	0.01	0.01	50	9	120	9	0.01	3	0.2	0.9	187	0.01
KL32-08	956.5	959.5	0.151		1510	0.03	0.01	29	6	2	15	0.01	3	0.2	0.9	200	0.01
KL32-08	959.5	962.1	0.21		2100	0.03	0.5	41	10	1	24	0.01	4	0.01	0.9	191	0.01
KL32-08	962.1	965.2	0.166		1660	0.02	0.6	54	20	30	24	0.01	2	0.4	1.2	147	0.01
KL32-08	965.2	967.9	0.23		2300	0.02	0.6	76	25	22	19	0.01	7	0.3	1.7	153	0.01
KL32-08	967.9	971.1	0.175		1750	0.03	0.6	38	9	1	13	0.01	4	0.2	1.1	172	0.01
KL32-08	971.1	974.2	0.194		1940	0.04	0.01	69	15	1	40	0.01	6	0.2	1.4	168	0.01
KL32-08	974.2	977.3	0.23		2300	0.03	0.01	60	14	1	16	0.01	5	0.2	1.2	139	0.01
KL32-08	977.3	980.5	0.29		2900	0.07	0.9	86	31	3	20	1	6	0.5	2.4	168	0.01
KL32-08	980.5	983.5	0.23		2300	0.04	0.8	165	28	5	22	0.01	5	0.01	1.4	128	0.01
KL32-08	983.5	985.7	0.27		2700	0.04	0.6	79	21	7	22	0.01	5	0.2	1.0	173	0.01
KL32-08	985.7	988.8	0.27		2700	0.05	0.7	46	11	15	42	0.01	4	0.5	0.8	148	0.01
KL32-08	988.8	992.8	0.33		3300	0.07	1.2	224	57	20	20	1	4	2.2	1.3	177	0.01
KL32-09	0	4.9	0.0304		304	0.02	0.6	670	121	13	7	0.01	0.01	0.9	1.8	38	0.01
KL32-09	4.9	8.5	0.0055		55	0.01	0.01	118	32	3	2	1	0.01	0.01	0.6	29	0.01
KL32-09	8.5	11.5	0.0046		46	0.01	0.01	106	57	3	3	0.01	0.01	0.01	0.5	30	0.01
KL32-09	11.5	14.5	0.0046		46	0.01	0.5	207	48	9	4	0.01	0.01	0.01	0.8	32	0.01
KL32-09	14.5	17.5	0.0085		85	0.01	0.01	102	35	5	6	0.01	0.01	0.01	1.1	33	0.01
KL32-09	17.5	19.9	0.0015		15	0.01	0.01	149	64	9	0.01	0.01	0.01	0.2	0.0	32	0.01
KL32-09	19.9	23.5	0.0028		28	0.01	0.01	136	62	7	3	0.01	0.01	0.2	1.1	51	0.01
KL32-09	23.5	26.5	0.26		2600	0.02	2.2	386	169	21	310	1	4	0.9	1.5	32	0.01
KL32-09	26.5	29.5	0.005		50	0.01	0.01	188	70	6	7	0.01	0.01	0.2	1.1	54	0.01
KL32-09	29.5	32.5	0.0076		76	0.01	0.01	124	47	10	6	0.01	0.01	0.3	2.6	51	0.01
KL32-09	32.5	35.5	0.0068		68	0.01	0.01	107	40	6	7	0.01	0.01	0.01	0.9	17	0.01
KL32-09	35.5	38.5	0.0087		87	0.01	0.5	58	27	4	2	0.01	0.01	0.01	0.9	18	0.01
KL32-09	38.5	41.5	0.0031		31	0.01	0.7	328	127	4	2	0.01	0.01	0.01	0.9	17	0.01
KL32-09	41.5	44.2	0.0029		29	0.01	0.6	287	150	6	0.01	0.01	0.01	0.6	1.8	21	0.01
KL32-09	44.2	47.3	0.0098		98	0.01	0.7	250	133	7	6	0.01	0.01	0.01	1.0	18	0.01
KL32-09	47.3	50.4	0.0042		42	0.01	0.01	94	56	4	3	0.01	2	0.01	2.0	15	0.01
KL32-09	50.4	53.5	0.0012		12	0.01	0.8	406	127	6	2	0.01	0.01	0.3	1.5	17	0.01
KL32-09	53.5	56.5	0.0036		36	0.01	1	386	223	14	3	0.01	0.01	0.4	1.4	23	0.01
KL32-09	56.5	59.5	0.0027		27	0.01	1	199	76	5	2	0.01	0.01	0.2	0.9	16	0.01
KL32-09	59.5	63.6	0.004		40	0.01	0.9	450	163	4	2	0.01	0.01	0.3	1.5	15	0.01
KL32-09	63.6	67.5	0.0046		46	0.01	0.01	313	195	4	2	0.01	0.01	0.4	2.0	17	0.01
KL32-09	67.5	71.5	0.0065		65	0.01	2	1180	1360	3	4	0.01	0.01	0.9	2.1	15	0.01
KL32-09	71.5	74.5	0.0114		114	0.01	5.9	3540	3400	13	7	0.01	0.01	3.9	7.0	23	0.2
KL32-09	74.5	77.5	0.0053		53	0.01	1.5	980	860	6	5	0.01	0.01	0.4	2.0	18	0.01
KL32-09	77.5	80.5	0.003		30	0.01	0.7	660	590	4	4	0.01	0.01	0.3	0.9	16	0.01
KL32-09	80.5	83.5	0.0031		31	0.01	0.6	363	317	5	5	1	0.01	0.01	1.6	16	0.01
KL32-09	83.5	86.5	0.0124		124	0.01	1	660	266	5	10	2	0.01	0.01	1.3	17	0.01
KL32-09	86.5	89.5	0.0073		73	0.01	4.2	1630	930	8	8	10	0.01	0.2	4.1	16	0.01
KL32-09	89.5	92.2	0.0311		311	0.01	12	6400	1210	29	12	26	3	0.6	6.0	15	0.13
KL32-09	92.2	95.3	0.016		160	0.02	1.8	1320	530	17	7	2	0.01	1.5	2.7	16	0.01
KL32-09	95.3	98.4	0.008		80	0.01	2.2	1130	550	15	30	5	0.01	0.01	3.8	12	0.01
KL32-09	98.4	101.4	0.0032		32	0.01	1.5	420	258	14	9	5	0.01	0.01	3.7	13	0.01
KL32-09	101.4	104.5	0.0112		112	0.01	1.6	271	360	11	8	4	0.01	0.01	3.5	13	0.01
KL32-09	104.5	107.5	0.0117		117	0.01	4.2	4320	2600	21	15	8	0.01	0.4	5.0	19	0.2
KL32-09	107.5	110.5	0.0043		43	0.01	1.7	470	570	13	11	5	0.01	0.01	2.3	13	0.01
KL32-09	110.5	113.5	0.004		40	0.01	2.8	1050	820	16	18	6	0.01	0.01	3.8	16	0.01
KL32-09	113.5	116.5	0.0063		63	0.01	1.9	406	460	22	18	3	0.01	0.2	6.3	16	0.1
KL32-09	116.5	119.3	0.0052		52	0.01	1.2	192	257	19	17	2	0.01	0.01	2.1	21	0.01
KL32-09	119.3	122.4	0.0276		276	0.01	5.9	1470	1110	80	55	10	3	3.3	4.0	20	0.01
KL32-09	122.4	125.5	0.054		540	0.02	13.8	4470	3800	180	117	24	15	4	10.0	27	0.12
KL32-09	125.5	128.5	0.0082		82	0.01	4.4	1630	3400	39	8	3	0.01	0.01	4.0	13	0.01
KL32-09	128.5	131.5	0.008		80	0.01	3.1	288	720	24	16	7	0.01	0.2	3.1	12	0.01
KL32-09	131.5	134.5	0.0024		24	0.01	1	133	152	13	24	2	0.01	0.2	2.5	13	0.01
KL32-09	134.5	137.5	0.043		430	0.01	1.4	730	387	16	33	3	0.01	1.1	3.5	14	0.01
KL32-09	137.5	140.5	0.0134		134	0.02	1.9	440	163	14	25	3	0.01	0.5	3.2	14	0.01
KL32-09	140.5	143.1	0.0049		49	0.03	2.9	3680	1220	40	12	3	0.01	2.9	6.5	18	0.1
KL32-09	143.1	146.1	0.0049		49	0.02	2.6	3390	1500	29	10	3	0.01	0.8	9.6	17	0.01
KL32-09	146.1	149.1	0.011		110	0.02	3.9	2230	800	45	140	4	4	2.9	7.3	17	0.1
KL32-09	149.1	152.3	0.0093		93	0.03	4.2	1470	1020	21	46	4	0.01	3.7	8.0	30	0.1

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL32-09	152.3	155.5	0.0042		42	0.01	1.6	374	351	9	23	0.01	0.01	0.6	2.8	19	0.01
KL32-09	155.5	158.5	0.0093		93	0.02	4.2	2280	2070	17	45	1	0.01	4.5	4.1	20	0.01
KL32-09	158.5	161.5	0.0272		272	0.01	1.2	327	300	7	26	0.01	0.01	0.5	1.9	23	0.01
KL32-09	161.5	164.5	0.0092		92	0.01	2.2	379	850	14	62	2	0.01	0.5	2.2	25	0.01
KL32-09	164.5	167.5	0.021		210	0.02	4	2580	4200	48	132	3	0.01	3.7	10.1	26	0.1
KL32-09	167.5	170.5	0.0327		327	0.01	4.5	1320	4600	54	87	5	0.01	3.2	5.0	19	0.01
KL32-09	170.5	173.5	0.026		260	0.01	4.8	690	2300	53	117	8	0.01	1.4	5.8	18	0.01
KL32-09	173.5	176.5	0.13		1300	0.01	48	2040	9800	56	574	94	0.01	2.7	18.6	23	0.1
KL32-09	176.5	179.5	0.13		1300	0.01	17.2	3450	6800	82	612	32	2	2.7	10.8	29	0.01
KL32-09	179.5	182.5	0.0187		187	0.01	3.1	1460	1750	17	128	6	0.01	0.4	4.2	30	0.01
KL32-09	182.5	185.5	0.0166		166	0.01	3.1	630	700	20	9	6	0.01	0.5	4.0	22	0.01
KL32-09	185.5	188.5	0.024		240	0.01	4.4	890	620	30	39	10	2	0.7	3.0	21	0.01
KL32-09	188.5	191.3	0.0265		265	0.01	3.5	490	580	55	29	6	0.01	2.5	5.5	39	0.01
KL32-09	191.3	194.4	0.079		790	0.01	4.4	990	1260	190	28	8	2	5.1	6.0	25	0.01
KL32-09	194.4	196.7	0.0278		278	0.01	1.8	118	240	75	31	2	3	2.5	4.2	20	0.01
KL32-09	196.7	200.5	0.0299		299	0.01	2.6	420	570	61	34	4	0.01	1.9	5.8	24	0.01
KL32-09	200.5	203.3	0.085		850	0.01	5	2810	3150	44	68	9	0.01	2.4	10.0	19	0.1
KL32-09	203.3	206.5	0.071		710	0.01	11.8	31200	27200	17	9	8	0.01	4	12.0	19	0.01
KL32-09	206.5	210.6	0.27		2700	0.01	52	19000	13100	200	143	110	4	13.4	33.0	30	0.24
KL32-09	210.6	213.1	0.053		530	0.01	10.9	2540	1300	79	15	26	3	2.6	9.0	14	0.01
KL32-09	213.1	215.5	0.083		830	0.01	13.8	10200	9900	80	6	23	6	4	18.2	12	0.01
KL32-09	215.5	218.4	0.054		540	0.01	4.4	660	1330	45	20	7	5	2.4	4.5	11	0.01
KL32-09	218.4	220.7	0.042		420	0.01	7.2	8100	6300	23	32	8	3	1.1	6.8	15	0.1
KL32-09	220.7	223.4	0.018		180	0.01	0.6	102	107	6	11	2	0.01	0.01	1.7	10	0.01
KL32-09	223.4	226.8	0.066		660	0.01	3.4	640	240	57	16	7	10	2.6	2.2	14	0.01
KL32-09	226.8	229.5	0.067		670	0.01	2.4	500	289	44	9	5	28	1.5	3.2	15	0.01
KL32-09	229.5	233.1	0.078		780	0.01	2	248	160	39	30	4	39	1.6	2.2	17	0.01
KL32-09	233.1	236.5	0.4		4000	0.01	6.8	1540	530	510	42	18	71	18	7.8	38	0.1
KL32-09	236.5	239.5	0.81		8100	0.33	1.1	102	50	0.01	97	0.01	29	0.01	7.0	62	0.1
KL32-09	239.5	242.5	2.34		23400	0.14	18.3	1690	640	41	2435	4	37	7.8	9.0	59	0.1
KL32-09	242.5	245.5	2.41		24100	0.14	13.2	2900	351	44	1225	5	49	7.9	25.0	82	0.1
KL32-09	245.5	248.5	2.2		22000	0.12	12.8	14700	3600	49	680	7	79	21	40.0	82	0.01
KL32-09	248.5	251.5	2.5		25000	0.16	3.5	1510	286	5	2880	2	47	0.5	26.0	34	0.01
KL32-09	251.5	254.8	2.06		20600	0.16	5.4	630	180	14	1072	6	65	3	25.0	53	0.01
KL32-09	254.8	257.7	0.23		2300	0.03	0.8	530	181	9	83	2	41	0.4	8.5	18	0.1
KL32-09	257.7	260.5	0.97		9700	0.08	1.6	2700	219	15	134	4	146	1.5	11.5	30	0.01
KL32-09	260.5	263.5	1.42		14200	0.14	2.4	3400	256	25	346	4	175	2.3	10.0	25	0.1
KL32-09	263.5	266.5	0.98		9800	0.12	2.1	520	228	27	242	6	144	2.3	24.5	33	0.3
KL32-09	266.5	269.5	1.03		10300	0.14	1.7	1440	133	17	209	5	101	2.5	21.8	27	0.2
KL32-09	269.5	272.5	2.92		29200	0.2	3.2	1150	280	9	1940	4	81	1.7	39.5	44	0.01
KL32-09	272.5	275.5	2.38		23800	0.16	3.8	1660	870	17	1455	5	52	1.2	18.5	36	0.01
KL32-09	275.5	278.5	1.34		13400	0.16	1.9	570	730	15	59	3	62	1.9	18.5	39	0.01
KL32-09	278.5	281.5	3.65		36500	0.34	3.1	820	363	6	1320	1	53	0.9	27.0	27	0.01
KL32-09	281.5	284.5	1.67		16700	0.2	1.8	510	280	3	451	0.01	43	0.7	13.0	24	0.01
KL32-09	284.5	287.5	1.04		10400	0.22	0.9	243	95	4	345	0.01	36	0.7	10.5	41	0.01
KL32-09	287.5	290.5	0.66		6600	0.15	0.6	115	198	2	194	0.01	26	0.2	6.4	45	0.01
KL32-09	290.5	293.5	0.73		7300	0.15	0.9	102	61	4	178	0.01	15	0.01	5.5	34	0.01
KL32-09	293.5	296.5	0.25		2500	0.09	0.01	96	81	4	197	0.01	13	0.3	2.5	30	0.01
KL32-09	296.5	299.5	0.88		8800	0.22	0.8	196	254	11	58	0.01	32	0.4	5.3	43	0.01
KL32-09	299.5	302.5	2.45		24500	0.48	2	358	283	6	550	0.01	31	0.5	16.0	50	0.01
KL32-09	302.5	305.5	1.72		17200	0.32	5.7	440	900	22	550	2	25	1.4	12.0	47	0.01
KL32-09	305.5	308.5	2.17		21700	0.55	4.4	470	189	14	670	2	35	1.2	20.0	69	0.01
KL32-09	308.5	311.5	2.8		28000	0.61	5.8	540	59	4	265	0.01	41	0.01	14.5	84	0.01
KL32-09	311.5	314.5	1.23		12300	0.45	3.2	372	87	9	146	1	28	0.2	7.5	68	0.01
KL32-09	314.5	317.5	0.52		5200	0.19	0.9	106	41	2	58	0.01	42	0.01	7.0	61	0.01
KL32-09	317.5	320.5	1.43		14300	0.1	16.8	2200	1120	200	740	8	51	7.9	6.0	64	0.01
KL32-09	320.5	323.5	2.3		23000	1	2.3	286	45	5	660	2	32	0.01	33.0	108	0.01
KL32-09	323.5	326.5	1.35		13500	0.45	3	1550	41	6	450	2	25	0.01	17.0	101	0.01
KL32-09	326.5	329.5	1.27		12700	0.47	1.3	470	40	3	311	1	34	0.01	14.5	104	0.01
KL32-09	329.5	332.5	1.07		10700	0.44	4.2	265	62	5	298	1	24	0.01	7.5	146	0.01
KL32-09	332.5	335.5	1.25		12500	0.55	5.7	930	66	12	231	6	34	0.4	8.5	96	0.01
KL32-09	335.5	338.5	2.5		25000	1.01	10.4	381	34	6	401	3	47	0.4	28.0	127	0.01
KL32-09	338.5	341.5	1.43		14300	1.03	7	73	23	18	168	2	17	0.6	4.5	98	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL32-09	341.5	344.5	0.97	9700	0.49	4.3	101	37	5	172	1	16	0.01	2.7	66	0.01
KL32-09	344.5	346.8	0.91	9100	0.32	5.7	129	43	3	162	4	17	0.2	3.8	69	0.01
KL32-09	346.8	349	0.79	7900	0.25	4	189	35	4	178	5	16	0.6	4.8	113	0.01
KL32-09	349	351.7	0.25	2500	0.06	1.4	147	36	12	402	2	12	0.9	2.4	174	0.01
KL32-09	351.7	354.3	0.105	1050	0.03	0.7	69	15	3	206	1	5	0.3	1.8	223	0.01
KL32-09	354.3	356.5	0.59	5900	0.15	2.3	102	25	3	156	2	12	0.01	2.8	137	0.01
KL32-09	356.5	359.5	0.58	5800	0.19	3.8	321	170	9	201	24	9	0.4	8.9	49	0.01
KL32-09	359.5	362.5	0.48	4800	0.29	4.6	550	387	11	89	36	11	0.4	17.8	53	0.01
KL32-09	362.5	365.5	2.76	27600	0.77	6.7	450	200	10	173	2	31	0.3	9.0	77	0.01
KL32-09	365.5	368.5	0.46	4600	0.25	1.6	113	36	9	182	0.01	10	0.2	2.3	76	0.01
KL32-09	368.5	371.5	0.72	7200	0.38	4.8	335	102	4	298	6	13	0.2	3.3	46	0.01
KL32-09	371.5	374.5	0.27	2700	0.24	4.7	396	343	12	140	20	14	0.6	19.5	43	0.01
KL32-09	374.5	377.5	0.49	4900	0.33	4.8	1030	550	15	105	6	18	0.5	24.4	51	0.01
KL32-09	377.5	380.5	0.23	2300	0.36	1.9	440	42	3	137	3	8	0.01	10.3	76	0.01
KL32-09	380.5	383.5	0.76	7600	0.44	3.5	1160	270	22	299	1	11	0.6	4.3	67	0.01
KL32-09	383.5	386.5	1.65	16500	0.64	9.5	680	302	5	474	5	12	1	4.5	120	0.01
KL32-09	386.5	389.5	0.7	7000	0.41	4.1	63	11	5	76	4	34	0.2	8.0	61	0.01
KL32-09	389.5	392.5	0.82	8200	0.73	3.9	57	13	3	130	2	13	0.01	7.5	41	0.01
KL32-09	392.5	395.2	0.47	4700	0.53	2.3	91	32	2	37	1	11	0.01	5.5	70	0.01
KL32-09	395.2	398.5	0.8	8000	0.67	3.4	116	44	14	35	2	14	1.6	4.3	115	0.01
KL32-09	398.5	401.5	3.67	36700	1.36	17.8	220	233	82	87	5	10	11.1	21.0	172	0.01
KL32-09	401.5	404.5	1.3	13000	0.93	4.9	71	20	5	43	2	19	0.4	4.0	98	0.01
KL32-09	404.5	407.5	0.99	9900	0.45	4.6	147	38	9	20	3	21	1.8	5.8	79	0.01
KL32-09	407.5	410.5	1.23	12300	0.76	5.7	72	25	5	53	2	15	0.5	6.0	137	0.01
KL32-09	410.5	413.5	1.28	12800	1.64	6.5	61	37	4	46	3	30	0.2	10.0	140	0.01
KL32-09	413.5	416.5	1.15	11500	0.91	4.2	56	18	2	36	2	14	0.01	8.0	98	0.01
KL32-09	416.5	419.5	1.17	11700	0.8	1.8	81	55	3	154	1	27	0.2	8.7	85	0.01
KL32-09	419.5	422.5	0.58	5800	0.23	0.8	62	26	1	390	0.01	13	0.3	8.3	218	0.01
KL32-09	422.5	425.5	0.65	6500	0.19	0.9	36	21	1	374	0.01	7	0.01	5.8	115	0.01
KL32-09	425.5	428.5	0.66	6600	0.2	0.8	46	17	0.01	208	0.01	7	0.01	5.0	142	0.01
KL32-09	428.5	431.5	0.65	6500	0.18	1	34	17	0.01	176	0.01	5	0.01	3.3	136	0.01
KL32-09	431.5	434.5	0.63	6300	0.15	1.2	71	48	1	141	0.01	9	0.2	4.5	150	0.01
KL32-09	434.5	437.5	0.54	5400	0.16	0.7	56	19	0.01	70	0.01	5	0.01	4.3	87	0.01
KL32-09	437.5	440.5	0.65	6500	0.14	0.9	276	115	2	110	0.01	5	0.5	3.3	243	0.01
KL32-09	440.5	443.5	0.77	7700	0.21	1.6	66	29	0.01	268	0.01	8	0.01	2.8	89	0.01
KL32-09	443.5	446.5	0.77	7700	0.18	0.9	51	17	0.01	133	0.01	7	0.3	1.8	69	0.01
KL32-09	446.5	449.5	0.64	6400	0.17	1.3	161	48	0.01	122	1	26	0.01	5.9	88	0.01
KL32-09	449.5	452.5	0.62	6200	0.25	1	25	14	0.01	130	0.01	11	0.01	5.8	58	0.01
KL32-09	452.5	455.5	0.52	5200	0.24	0.8	24	15	1	66	0.01	13	0.01	9.8	100	0.01
KL32-09	455.5	458.5	1.04	10400	0.36	1.8	24	22	0.01	87	0.01	15	0.01	7.5	66	0.01
KL32-09	458.5	461.5	0.82	8200	0.53	1.7	41	12	0.01	117	0.01	21	0.01	13.0	84	0.01
KL32-09	461.5	464.5	1.27	12700	0.57	2.4	23	14	1	51	0.01	24	0.01	8.0	52	0.01
KL32-09	464.5	467.5	1.35	13500	0.87	3.6	30	18	3	23	0.01	26	0.01	16.0	56	0.01
KL32-09	467.5	470.5	1.1	11000	0.81	2.3	32	16	7	36	0.01	19	0.2	11.0	92	0.01
KL32-09	470.5	473.5	1.18	11800	0.71	2	56	27	6	42	1	31	0.2	12.5	107	0.01
KL32-09	473.5	475.8	0.76	7600	0.36	1.9	36	20	4	16	1	23	0.4	12.5	67	0.01
KL32-09	475.8	479.5	1.1	11000	0.94	3.3	45	26	10	12	1	80	0.3	21.3	98	0.01
KL32-09	479.5	482.5	1.14	11400	1.18	7.2	93	115	28	61	3	85	0.2	25.5	95	0.01
KL32-09	482.5	485.5	0.67	6700	0.54	2.2	38	30	21	186	1	45	0.01	15.5	117	0.01
KL32-09	485.5	488.5	0.81	8100	0.82	2.4	49	27	12	47	1	50	0.01	9.8	105	0.01
KL32-09	488.5	491.5	0.69	6900	0.6	2	42	29	8	79	1	64	0.2	10.3	90	0.01
KL32-09	491.5	494.5	0.6	6000	0.84	1.2	40	35	41	56	1	56	0.4	7.5	100	0.01
KL32-09	494.5	497.5	0.75	7500	1	2	50	24	16	35	2	34	0.3	10.3	96	0.01
KL32-09	497.5	500.5	1.06	10600	1.02	3.7	184	19	11	65	1	40	0.3	11.3	103	0.01
KL32-09	500.5	503.5	1.14	11400	1.2	5.3	259	40	0.01	50	0.01	54	0.2	10.0	65	0.01
KL32-09	503.5	506.5	1.29	12900	1.18	3.3	173	15	1	42	1	45	0.5	13.5	62	0.01
KL32-09	506.5	509.5	1.55	15500	1.4	2.9	219	16	17	10	1	54	0.8	19.5	74	0.01
KL32-09	509.5	512.5	2.54	25400	2.94	3.4	258	20	48	5	0.01	47	1.2	9.5	95	0.01
KL32-09	512.5	515.5	5.69	56900	4.38	8	335	19	9	133	0.01	114	0.9	17.0	150	0.01
KL32-09	515.5	518.5	3.16	31600	2.08	4.8	412	68	80	31	0.01	53	1.1	9.0	113	0.01
KL32-09	518.5	521.5	2.21	22100	1.36	2.8	334	57	33	15	1	44	1.5	21.0	92	0.01
KL32-09	521.5	524.3	2.71	27100	1.74	3	356	91	35	76	0.01	47	1.4	7.0	140	0.01
KL32-09	524.3	527.5	1.33	13300	0.92	1.7	273	18	8	36	0.01	44	0.01	10.0	102	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL32-09	527.5	530.5	3.43	34300	2.02	4.1	368	21	19	91	0.01	57	2.1	8.0	126	0.01
KL32-09	530.5	533.5	10.9	109000	8.91	19.8	1080	17	21	1840	0.01	88	0.6	17.5	87	0.01
KL32-09	533.5	536.5	5.52	55200	4.48	15.8	640	12	9	196	1	84	0.2	20.0	96	0.01
KL32-09	536.5	539.5	4.2	42000	3.24	15.5	321	15	17	39	1	83	0.2	17.5	92	0.01
KL32-09	539.5	542.5	1.21	12100	0.77	2.3	47	11	21	141	1	70	0.01	13.5	84	0.01
KL32-09	542.5	545.5	5.46	54600	7.82	9.7	174	9	15	86	1	87	0.01	8.0	127	0.01
KL32-09	545.5	548.5	2.46	24600	4.12	5.6	208	16	15	69	1	60	0.2	14.0	147	0.01
KL32-09	548.5	551.5	1.54	15400	1.84	3.4	231	15	9	90	1	57	0.01	11.5	110	0.01
KL32-09	551.5	554.5	3.63	36300	4.24	8.4	244	11	13	106	1	90	0.01	12.5	146	0.01
KL32-09	554.5	557.5	0.88	8800	0.48	1.9	31	10	29	49	0.01	46	0.01	9.0	105	0.01
KL32-09	557.5	560.5	0.82	8200	0.69	2.2	43	10	9	64	1	23	0.01	7.3	95	0.01
KL32-09	560.5	563.5	1.14	11400	0.49	2.7	47	30	10	42	0.01	59	0.01	16.0	120	0.01
KL32-09	563.5	566.5	1.58	15800	0.77	3.1	56	13	17	108	1	59	0.01	10.0	146	0.01
KL32-09	566.5	568.8	1.89	18900	0.8	3.3	41	12	12	51	1	80	0.01	11.0	140	0.01
KL32-09	568.8	572.5	0.55	5500	0.2	0.6	16	8	0.01	129	0.01	47	0.01	5.8	93	0.01
KL32-09	572.5	575.5	0.53	5300	0.17	0.6	24	9	0.01	78	0.01	45	0.01	5.0	98	0.01
KL32-09	575.5	578.5	1	10000	0.23	1	39	14	0.01	114	0.01	15	0.01	4.6	90	0.01
KL32-09	578.5	581.5	0.79	7900	0.18	0.8	41	17	1	123	0.01	12	0.01	3.5	107	0.01
KL32-09	581.5	584.5	0.73	7300	0.19	0.7	33	16	1	175	0.01	7	0.01	3.3	96	0.01
KL32-09	584.5	587.5	0.56	5600	0.2	0.7	23	7	0.01	102	0.01	6	0.01	3.0	70	0.01
KL32-09	587.5	590.5	0.55	5500	0.2	1.1	13	7	0.01	621	0.01	5	0.01	2.6	73	0.01
KL32-09	590.5	593.5	0.78	7800	0.25	1.2	14	6	0.01	248	0.01	6	0.01	2.3	87	0.01
KL32-09	593.5	596.5	0.84	8400	0.2	1	59	17	1	280	0.01	4	0.01	2.8	96	0.01
KL32-09	596.5	599.5	0.74	7400	0.23	0.7	28	10	0.01	308	0.01	4	0.01	2.8	120	0.01
KL32-09	599.5	602.5	0.75	7500	0.29	0.7	22	5	0.01	275	0.01	3	0.01	2.3	118	0.01
KL32-09	602.5	605.5	0.67	6700	0.27	1.1	15	6	0.01	300	0.01	4	0.01	2.5	81	0.01
KL32-09	605.5	608.5	0.58	5800	0.24	1	21	6	0.01	214	0.01	4	0.01	3.3	76	0.01
KL32-09	608.5	611.5	0.8	8000	0.39	1.2	18	5	0.01	190	0.01	5	0.01	1.9	58	0.01
KL32-10	0	2.5	0.0028	28	0.01	0.01	217	51	5	3	0.01	0.01	0.5	1.3	14	0.01
KL32-10	2.5	5.5	0.0045	45	0.01	0.01	107	41	7	3	0.01	0.01	0.3	1.2	16	0.01
KL32-10	5.5	8.5	0.0018	18	0.02	0.01	129	39	4	4	0.01	0.01	1.1	1.3	21	0.01
KL32-10	8.5	11.2	0.0038	38	0.02	0.01	160	38	4	3	0.01	0.01	0.6	0.9	19	0.01
KL32-10	11.2	14.1	0.0026	26	0.02	0.01	157	52	4	4	0.01	0.01	0.8	0.8	16	0.01
KL32-10	14.1	17.5	0.0022	22	0.01	0.01	193	42	3	4	0.01	0.01	0.7	1.7	16	0.01
KL32-10	17.5	19.9	0.002	20	0.02	0.01	109	49	2	3	0.01	0.01	0.5	1.4	15	0.01
KL32-10	19.9	23.5	0.0015	15	0.02	0.01	239	58	3	3	0.01	0.01	0.8	1.2	19	0.01
KL32-10	23.5	27.3	0.0012	12	0.03	0.01	179	47	2	4	0.01	0.01	0.7	1.8	20	0.01
KL32-10	27.3	29.5	0.0073	73	0.03	0.01	88	31	2	5	0.01	0.01	0.4	0.8	20	0.01
KL32-10	29.5	32.6	0.0047	47	0.03	0.01	142	48	3	3	0.01	0.01	0.3	1.3	22	0.01
KL32-10	32.6	35.2	0.0017	17	0.02	0.01	123	29	4	2	0.01	0.01	0.7	1.5	17	0.01
KL32-10	35.2	38.5	0.0036	36	0.01	0.01	106	25	2	3	0.01	0.01	0.7	1.1	19	0.01
KL32-10	38.5	41.5	0.0016	16	0.03	0.01	195	56	4	3	0.01	0.01	0.3	1.1	15	0.01
KL32-10	41.5	45.8	0.0043	43	0.01	0.01	82	24	3	0.01	0.01	0.01	0.2	1.0	25	0.01
KL32-10	45.8	48.6	0.0008	8	0.01	0.01	57	16	3	2	0.01	0.01	0.4	0.7	23	0.01
KL32-10	48.6	50.5	0.0029	29	0.01	0.01	56	15	6	3	0.01	0.01	0.5	1.2	28	0.01
KL32-10	50.5	53.5	0.0026	26	0.01	0.01	34	11	4	2	0.01	0.01	0.01	1.0	29	0.01
KL32-10	53.5	56.5	0.0023	23	0.01	0.01	67	19	6	3	0.01	0.01	0.9	0.5	26	0.01
KL32-10	56.5	59.5	0.001	10	0.04	0.01	190	40	4	4	0.01	0.01	1.7	1.3	21	0.01
KL32-10	59.5	62.1	0.0035	35	0.03	0.01	88	20	5	4	1	0.01	1.4	1.3	31	0.01
KL32-10	62.1	65.5	0.0031	31	0.01	0.01	77	20	5	4	0.01	0.01	0.4	1.1	25	0.01
KL32-10	65.5	68.4	0.0014	14	0.06	0.5	470	31	6	2	0.01	0.01	2.3	1.7	23	0.19
KL32-10	68.4	71.5	0.0019	19	0.05	0.01	267	39	8	3	0.01	0.01	0.9	1.3	20	0.1
KL32-10	71.5	73.4	0.0014	14	0.04	0.01	105	29	4	0.01	0.01	0.01	2.4	1.1	23	0.01
KL32-10	73.4	75.4	0.0017	17	0.03	0.01	92	19	3	3	0.01	0.01	0.9	1.3	20	0.01
KL32-10	75.4	78.4	0.0014	14	0.02	0.01	60	19	2	2	0.01	0.01	0.5	0.7	21	0.01
KL32-10	78.4	81.9	0.0009	9	0.07	0.01	95	30	3	2	0.01	0.01	0.8	1.5	31	0.01
KL32-10	81.9	84.7	0.0017	17	0.03	0.01	60	16	4	2	0.01	0.01	0.01	0.8	20	0.01
KL32-10	84.7	87.6	0.0019	19	0.02	0.01	57	18	3	3	0.01	0.01	0.3	0.7	19	0.01
KL32-10	87.6	90.7	0.0021	21	0.01	0.01	42	12	5	4	0.01	0.01	0.01	1.4	19	0.01
KL32-10	90.7	92.5	0.0035	35	0.01	0.01	45	15	3	4	0.01	0.01	0.2	0.6	20	0.01
KL32-10	92.5	95.5	0.0015	15	0.02	0.01	35	23	11	6	0.01	0.01	0.8	1.6	46	0.01
KL32-10	95.5	98	0.0037	37	0.06	0.01	45	17	6	6	0.01	0.01	0.4	1.1	55	0.01
KL32-10	98	101.5	0.0022	22	0.15	0.01	130	26	7	3	0.01	0.01	0.7	1.0	49	0.1

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL32-10	101.5	104.5	0.0019		19	0.17	0.01	155	23	13	6	0.01	0.01	0.8	1.3	42	0.1
KL32-10	104.5	107.5	0.0118		118	0.29	0.01	93	20	16	6	0.01	0.01	1.4	1.2	35	0.1
KL32-10	107.5	110.4	0.0059		59	0.08	0.01	67	19	5	4	0.01	0.01	0.5	0.5	28	0.11
KL32-10	110.4	113.5	0.0078		78	0.03	0.01	43	17	5	3	0.01	0.01	0.2	0.6	30	0.01
KL32-10	113.5	116.5	0.0086		86	0.14	0.01	51	16	7	3	0.01	0.01	0.4	0.7	40	0.01
KL32-10	116.5	119.5	0.0038		38	0.08	0.01	76	25	5	3	0.01	0.01	0.8	0.7	28	0.1
KL32-10	119.5	122.5	0.003		30	0.06	0.01	32	16	6	4	0.01	0.01	0.3	1.0	20	0.01
KL32-10	122.5	125.5	0.0037		37	0.01	0.01	23	24	2	0.01	0.01	0.01	0.4	0.0	25	0.01
KL32-10	125.5	128.5	0.0025		25	0.01	0.01	25	11	5	3	0.01	0.01	0.3	1.1	19	0.01
KL32-10	128.5	131.5	0.002		20	0.01	0.01	29	12	7	3	0.01	0.01	0.5	1.3	24	0.01
KL32-10	131.5	134.8	0.0017		17	0.02	0.01	29	13	7	2	0.01	0.01	0.5	1.5	29	0.01
KL32-10	134.8	137.5	0.001		10	0.01	0.01	16	10	8	2	0.01	0.01	0.3	1.2	20	0.01
KL32-10	137.5	140.5	0.0019		19	0.01	0.01	24	15	11	4	0.01	0.01	0.7	1.0	20	0.01
KL32-10	140.5	143.5	0.0019		19	0.03	0.01	21	17	10	2	0.01	0.01	0.6	0.9	19	0.01
KL32-10	143.5	146.5	0.0025		25	0.01	0.01	22	14	17	4	0.01	0.01	1.1	1.0	20	0.01
KL32-10	146.5	149.5	0.0014		14	0.04	0.01	32	24	12	4	0.01	0.01	1.9	2.0	26	0.01
KL32-10	149.5	152.5	0.0028		28	0.17	0.01	24	19	13	3	0.01	0.01	1.8	2.6	22	0.01
KL32-10	152.5	155.4	0.0018		18	0.06	0.01	13	13	7	2	0.01	0.01	0.8	1.1	18	0.01
KL32-10	155.4	158.5	0.0011		11	0.08	0.01	16	12	15	3	0.01	0.01	0.7	1.6	18	0.01
KL32-10	158.5	161.4	0.002		20	0.01	0.01	15	15	8	2	0.01	0.01	0.9	1.0	20	0.01
KL32-10	161.4	164.4	0.0014		14	0.02	0.01	41	16	15	6	0.01	0.01	0.9	1.2	22	0.01
KL32-10	164.4	167.5	0.001		10	0.01	0.01	15	13	15	3	0.01	0.01	0.8	1.3	15	0.01
KL32-10	167.5	170.5	0.0018		18	0.03	0.01	21	14	13	2	0.01	0.01	1.4	1.3	19	0.01
KL32-10	170.5	173.5	0.0044		44	0.23	0.7	28	23	5	6	0.01	0.01	3.2	1.7	29	0.01
KL32-10	173.5	176.5	0.0033		33	0.15	0.6	50	28	15	4	0.01	0.01	2	1.6	23	0.01
KL32-10	176.5	179.5	0.0026		26	0.18	0.6	54	28	14	3	0.01	0.01	2.5	1.1	17	0.1
KL32-10	179.5	182.5	0.0019		19	0.2	0.5	30	20	21	4	0.01	0.01	1.6	2.2	18	0.1
KL32-10	182.5	184.7	0.0041		41	0.07	0.01	31	23	14	4	0.01	0.01	1.6	2.6	22	0.01
KL32-10	184.7	187.7	0.003		30	0.08	0.01	29	23	12	0.01	0.01	0.01	1.5	3.2	20	0.01
KL32-10	187.7	190.5	0.0031		31	0.04	0.01	26	22	8	0.01	0.01	0.01	1.5	1.4	14	0.01
KL32-10	190.5	194.5	0.0014		14	0.03	0.01	37	31	8	0.01	0.01	0.01	1.2	1.1	15	0.01
KL32-10	194.5	197.5	0.0008		8	0.01	0.01	55	86	12	2	0.01	0.01	1	1.7	15	0.01
KL32-10	197.5	200.5	0.0015		15	0.05	0.01	243	77	21	3	0.01	0.01	2.5	3.3	20	0.01
KL32-10	200.5	203.2	0.0142		142	0.17	13.5	5500	10400	160	5	0.01	0.01	32	61.0	24	0.5
KL32-10	203.2	206.2	0.0164		164	0.05	1.6	192	1110	50	4	0.01	3	5.2	4.8	27	0.01
KL32-10	206.2	210	0.0095		95	0.05	0.6	195	124	74	3	0.01	0.01	3.7	2.7	19	0.01
KL32-10	210	212.5	0.0037		37	0.05	0.5	54	116	32	4	0.01	3	1.9	1.7	23	0.1
KL32-10	212.5	215.5	0.004		40	0.06	0.01	27	45	11	4	0.01	0.01	1.8	1.8	15	0.01
KL32-10	215.5	218.5	0.0034		34	0.04	0.01	21	27	13	4	0.01	2	1.4	2.7	21	0.01
KL32-10	218.5	221.5	0.0013		13	0.02	0.01	19	25	13	3	0.01	0.01	0.9	1.3	16	0.01
KL32-10	221.5	224.5	0.0066		66	0.04	0.01	52	28	13	3	0.01	0.01	1.8	1.2	20	0.01
KL32-10	224.5	227.5	0.0091		91	0.01	0.01	62	53	10	2	0.01	0.01	1.4	0.8	30	0.01
KL32-10	227.5	230.5	0.0075		75	0.02	0.01	65	32	7	2	0.01	0.01	1.7	1.5	53	0.01
KL32-10	230.5	233.5	0.0112		112	0.02	0.01	44	23	7	0.01	0.01	0.01	1.6	1.2	38	0.01
KL32-10	233.5	236.5	0.0109		109	0.02	0.5	45	22	4	2	0.01	2	1.5	0.7	38	0.01
KL32-10	236.5	239.4	0.005		50	0.04	0.5	85	46	6	2	0.01	0.01	3.1	1.5	25	0.01
KL32-10	239.4	242.9	0.006		60	0.02	0.01	41	32	6	2	0.01	0.01	0.9	2.1	28	0.01
KL32-10	242.9	245.4	0.0109		109	0.05	1.2	117	105	32	3	0.01	0.01	3.1	3.5	17	0.01
KL32-10	245.4	248.4	0.007		70	0.04	0.01	37	23	9	3	0.01	0.01	0.8	1.6	31	0.01
KL32-10	248.4	251.6	0.0083		83	0.02	0.01	25	16	6	3	0.01	2	0.6	1.3	26	0.01
KL32-10	251.6	254.5	0.0051		51	0.01	0.01	22	12	4	2	0.01	2	0.5	1.2	27	0.01
KL32-10	254.5	257.5	0.0012		12	0.01	0.01	20	10	7	2	0.01	2	0.8	1.0	38	0.01
KL32-10	257.5	260.5	0.0011		11	0.13	0.01	29	18	10	3	0.01	0.01	1.6	1.6	38	0.01
KL32-10	260.5	263.5	0.0041		41	0.01	0.6	23	15	11	3	0.01	3	1.4	1.0	21	0.01
KL32-10	263.5	266.5	0.0013		13	0.15	0.01	35	17	17	4	0.01	2	1.5	1.9	21	0.01
KL32-10	266.5	269.5	0.0013		13	0.06	0.01	29	19	22	5	0.01	2	1.3	1.0	28	0.01
KL32-10	269.5	272.3	0.0015		15	0.13	0.01	35	16	20	4	0.01	3	1.2	1.4	24	0.01
KL32-10	272.3	275.4	0.0009		9	0.02	0.01	25	19	20	4	0.01	3	2.1	1.2	22	0.01
KL32-10	275.4	278.5	0.0016		16	0.02	0.01	36	25	20	6	0.01	2	1.9	2.6	19	0.01
KL32-10	278.5	281.5	0.0018		18	0.01	0.01	19	21	17	8	0.01	0.01	2.7	2.3	24	0.01
KL32-10	281.5	284.5	0.0064		64	0.04	0.01	59	40	24	5	0.01	2	2.2	3.1	23	0.01
KL32-10	284.5	287.5	0.0051		51	0.02	0.01	47	15	17	6	0.01	2	1.4	3.1	22	0.01
KL32-10	287.5	290.5	0.041		410	0.05	0.6	76	16	25	5	0.01	3	1	2.4	21	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL32-10	290.5	293.5	0.0118		118	0.03	0.01	40	14	25	5	0.01	2	1	1.4	21	0.13
KL32-10	293.5	296.5	0.0061		61	0.01	0.01	26	17	21	5	0.01	2	0.9	1.1	30	0.01
KL32-10	296.5	299.5	0.0188		188	0.01	0.01	37	13	22	5	0.01	3	0.5	0.9	35	0.01
KL32-10	299.5	302.5	0.0055		55	0.01	0.01	47	14	25	5	0.01	0.01	0.7	1.0	31	0.01
KL32-10	302.5	305.3	0.0037		37	0.01	0.01	30	21	15	6	0.01	3	0.8	1.9	28	0.01
KL32-10	305.3	308.4	0.007		70	0.01	0.01	26	14	20	3	0.01	2	0.6	1.7	30	0.01
KL32-10	308.4	311.4	0.0041		41	0.01	0.01	25	18	18	2	0.01	2	0.7	2.1	22	0.01
KL32-10	311.4	314.5	0.0017		17	0.01	0.01	21	12	21	3	0.01	2	0.5	1.7	21	0.01
KL32-10	314.5	317.7	0.0101		101	0.01	0.01	25	15	22	2	0.01	2	0.7	1.8	21	0.01
KL32-10	317.7	337.7															
KL32-10	337.7	365.2															
KL32-10	365.2	371.7															
KL32-10	371.7	380.2															
KL32-10	380.2	389.2															
KL32-10	389.2	404.2															
KL32-10	404.2	416.2															
KL32-10	416.2	422.2															
KL32-10	422.2	437.2															
KL32-10	437.2	477.2															
KL32-10	477.2	518.5															
KL32-11	0	2.7	0.0045		45	0.03	0.7	312	105	9	56	0.01	0.01	1.1	1.1	93	0.01
KL32-11	2.7	5.7	0.001		10	0.01	0.01	261	53	5	5	0.01	0.01	0.3	0.9	44	0.01
KL32-11	5.7	8.7	0.0011		11	0.01	0.01	264	96	11	4	0.01	2	0.6	1.8	32	0.01
KL32-11	8.7	11.7	0.0013		13	0.01	0.01	88	41	7	6	0.01	0.01	1.3	1.3	49	0.01
KL32-11	11.7	14.7	0.0014		14	0.01	0.5	245	59	8	5	1	0.01	0.4	1.2	32	0.01
KL32-11	14.7	17.7	0.0176		176	0.01	2.2	314	328	36	3	6	2	1.1	7.0	47	0.01
KL32-11	17.7	20.7	0.0017		17	0.01	0.01	67	46	14	6	0.01	0.01	0.9	1.6	32	0.01
KL32-11	20.7	23.7	0.0014		14	0.01	0.01	142	86	14	7	1	0.01	1	1.5	42	0.01
KL32-11	23.7	26.7	0.0013		13	0.01	0.01	136	79	15	6	1	0.01	0.4	1.5	57	0.01
KL32-11	26.7	29.7	0.0012		12	0.01	0.5	299	104	10	6	1	0.01	0.5	3.0	15	0.01
KL32-11	29.7	32.7	0.0013		13	0.01	0.01	139	91	12	5	1	0.01	0.8	1.9	39	0.01
KL32-11	32.7	35.7	0.0019		19	0.01	0.01	52	43	11	4	0.01	0.01	0.5	1.1	26	0.01
KL32-11	35.7	38.7	0.0023		23	0.01	0.01	108	55	19	6	1	0.01	0.5	1.8	40	0.01
KL32-11	38.7	41.7	0.136		1360	0.04	0.9	450	202	14	11	1	3	0.7	3.1	29	0.01
KL32-11	41.7	44.7	0.0076		76	0.04	7.6	4100	2610	50	9	0.01	0.01	4.6	19.9	23	0.01
KL32-11	44.7	47.2	0.003		30	0.01	1.2	297	317	20	6	1	0.01	0.7	1.8	32	0.01
KL32-11	47.2	50.3	0.0016		16	0.06	1.3	440	740	27	6	1	0.01	1.2	1.5	22	0.01
KL32-11	50.3	53.4	0.0029		29	0.08	1.3	1020	790	24	6	1	2	1.5	1.7	26	0.01
KL32-11	53.4	56.5	0.0007		7	0.01	1	148	760	19	5	0.01	3	0.9	0.7	26	0.01
KL32-11	56.5	59.6	0.0015		15	0.31	0.7	1130	660	31	16	1	0.01	2.3	5.3	26	0.01
KL32-11	59.6	62.7	0.0113		113	0.29	2.3	1630	2060	33	12	2	0.01	3.5	6.0	29	0.01
KL32-11	62.7	65.7	0.0051		51	0.31	2.6	1620	2630	41	6	1	0.01	5	4.0	18	0.26
KL32-11	65.7	68.7	0.0056		56	0.23	2.8	3790	4000	46	5	1	0.01	5.5	13.3	22	0.16
KL32-11	68.7	71.7	0.0125		125	0.5	4.1	930	3320	120	36	6	3	6.8	15.5	53	0.28
KL32-11	71.7	74.7	0.0052		52	0.42	2.4	1520	1120	69	32	2	0.01	4	6.3	32	0.15
KL32-11	74.7	77.7	0.0043		43	0.26	1.4	730	335	52	14	2	0.01	1.7	3.0	23	0.18
KL32-11	77.7	80.7	0.0057		57	0.7	3.8	3600	1900	81	63	2	3	5.6	5.5	43	0.16
KL32-11	80.7	83.5	0.0022		22	0.07	0.6	460	142	25	15	1	0.01	1.1	2.0	26	0.01
KL32-11	83.5	85.9	0.0021		21	0.13	0.7	1550	550	39	8	2	0.01	2.8	2.5	25	0.01
KL32-11	85.9	88.8	0.0077		77	0.27	3.1	2630	1860	43	14	5	2	6.5	5.3	47	0.18
KL32-11	88.8	91	0.0043		43	0.31	2.5	3300	1670	74	14	5	2	4.5	9.4	29	0.18
KL32-11	91	92.5	0.0022		22	0.16	0.9	267	388	58	27	7	0.01	3.5	5.5	25	0.01
KL32-11	92.5	94.6	0.0083		83	0.1	1	402	264	70	27	8	0.01	1.8	3.5	26	0.01
KL32-11	94.6	97.6	0.0131		131	0.08	1.4	670	460	75	37	12	0.01	2	2.7	25	0.01
KL32-11	97.6	99.4	0.0062		62	0.68	2.1	800	378	70	60	7	2	5.9	6.1	49	0.17
KL32-11	99.4	101.7	0.0067		67	0.42	3	2160	1110	55	90	19	0.01	4.4	5.1	42	0.15
KL32-11	101.7	104.7	0.0061		61	0.16	5.1	5600	2900	41	82	15	0.01	2.6	4.5	43	0.01
KL32-11	104.7	107.7	0.0154		154	0.41	3.6	5200	2400	47	11	10	0.01	3	4.4	40	0.01
KL32-11	107.7	110.7	0.023		230	0.18	7.3	3020	3650	73	3	15	4	5	2.8	45	0.01
KL32-11	110.7	113.7	0.072		720	0.04	5.1	810	1120	18	230	12	5	1.8	9.0	34	0.01
KL32-11	113.7	116.7	0.161		1610	0.13	2.9	450	322	60	9	4	5	12.4	14.7	23	0.01
KL32-11	116.7	119.7	0.056		560	0.03	7.6	257	880	29	391	20	8	2.4	9.0	52	0.01
KL32-11	119.7	122.7	0.305		3050	0.11	7.8	170	440	120	620	15	9	3.6	12.8	149	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL32-11	122.7	125.2	0.078		780	0.08	2.6	266	358	80	1570	3	6	6.2	8.8	106	0.01
KL32-11	125.2	128.2	0.069		690	0.02	2.1	82	84	27	97	3	4	2.6	4.0	84	0.01
KL32-11	128.2	129.8	0.051		510	0.14	15	1420	1930	81	510	30	6	6.7	18.8	135	0.01
KL32-11	129.8	131.7	0.0372		372	0.03	1.3	193	510	21	67	2	6	1.6	2.7	141	0.01
KL32-11	131.7	134.5	0.0023		23	0.04	0.7	450	93	10	18	1	0.01	1.8	1.8	57	0.01
KL32-11	134.5	137.6	0.0171		171	0.04	1.2	261	670	21	57	1	4	1.6	2.6	189	0.01
KL32-11	137.6	140.7	0.095		950	0.09	2.5	262	410	89	1650	4	6	4.8	8.2	101	0.01
KL32-11	140.7	143.7	0.0009		9	0.01	0.01	248	45	6	4	0.01	0.01	0.2	0.6	46	0.01
KL32-11	143.7	146.7	0.191		1910	0.17	5.7	800	570	80	248	28	3	4.1	11.5	126	0.01
KL32-11	146.7	148.6	0.0214		214	0.02	0.7	150	118	45	34	2	4	2.4	4.8	206	0.01
KL32-11	148.6	151	0.054		540	0.04	2.1	710	590	120	112	2	7	5.2	2.8	145	0.01
KL32-11	151	152.3	0.0171		171	0.03	0.7	59	48	13	40	1	5	0.9	2.5	122	0.01
KL32-11	152.3	154.6	0.206		2060	0.13	10.7	720	990	75	118	40	6	4.6	21.1	85	0.01
KL32-11	154.6	157.7	0.256		2560	0.09	4.1	295	280	21	33	2	8	1.6	9.0	65	0.01
KL32-11	157.7	159.5	0.501		5010	0.24	23.8	800	1530	83	251	258	14	3.8	72.5	111	0.01
KL32-11	159.5	161.7	0.0031		31	0.05	0.6	395	99	13	34	0.01	0.01	2.4	1.5	59	0.01
KL32-11	161.7	164.7	0.174		1740	0.05	2.8	205	241	39	86	3	8	5	12.0	136	0.01
KL32-11	164.7	167	0.213		2130	0.08	4.6	343	510	43	89	11	7	4.8	22.0	109	0.01
KL32-11	167	169.8	0.17		1700	0.18	10.1	2720	2520	65	210	82	12	2.9	72.5	96	0.01
KL32-11	169.8	171.6	0.106		1060	0.04	2.4	262	263	100	35	0.01	3	3.8	4.8	145	0.01
KL32-11	171.6	173.7	0.312		3120	0.2	9.5	3750	2170	140	140	4	7	7.8	8.8	104	0.01
KL32-11	173.7	176.7	0.0344		344	0.08	1.8	293	374	42	248	1	6	2.5	2.6	82	0.01
KL32-11	176.7	179.7	0.32		3200	0.19	18.8	2400	8800	54	358	18	21	15.6	16.1	66	0.01
KL32-11	179.7	182.7	1.55		15500	0.41	29	6300	4800	600	254	21	30	12.9	5.0	112	0.01
KL32-11	182.7	184.8	0.146		1460	0.21	25	10900	14700	430	43	12	26	24.5	15.5	73	0.01
KL32-11	184.8	187.8	0.3		3000	0.31	67	21000	38100	1410	67	24	68	67	15.5	110	0.01
KL32-11	187.8	190.9	0.76		7600	0.52	27	2300	2300	150	486	32	19	6.2	37.5	72	0.01
KL32-11	190.9	194	0.37		3700	0.12	12.3	1520	1400	130	266	5	15	3.6	33.5	76	0.01
KL32-11	194	196.9	0.23		2300	0.16	56	73000	39500	120	52	21	10	60	42.0	38	0.1
KL32-11	196.9	198.2	0.131		1310	0.09	21.7	27900	10000	220	45	30	8	10	55.5	25	0.12
KL32-11	198.2	200.4	0.0202		202	0.09	3.2	4130	1320	31	24	4	0.01	3.5	8.5	18	0.01
KL32-11	200.4	202.9	0.142		1420	0.07	36	10700	20200	100	85	62	3	9.4	31.5	19	0.16
KL32-11	202.9	206	0.0276		276	0.04	11	4900	4800	43	21	18	0.01	6.3	7.0	28	0.01
KL32-11	206	209.3	0.0023		23	0.05	1.6	440	1050	25	11	0.01	0.01	2.4	1.8	24	0.01
KL32-11	209.3	212.4	0.0246		246	0.03	3.7	2250	1850	13	85	8	0.01	1.7	6.3	15	0.01
KL32-11	212.4	214.7	0.0259		259	0.04	1.3	770	740	8	17	3	2	1.2	4.0	15	0.01
KL32-11	214.7	217.8	0.0037		37	0.02	1.1	540	850	6	10	2	0.01	0.9	4.0	22	0.01
KL32-11	217.8	219.6	0.176		1760	0.13	3.8	1810	3010	23	17	6	3	3.6	8.5	31	0.01
KL32-11	219.6	221.1	0.0034		34	0.01	1	540	830	5	11	1	3	1	2.7	22	0.01
KL32-11	221.1	223.9	0.007		70	0.02	0.9	810	1400	6	8	2	2	1.6	2.6	20	0.01
KL32-11	223.9	225.1	0.06		600	0.01	1.7	156	379	10	15	1	0.01	1.2	1.5	72	0.01
KL32-11	225.1	227.3	0.087		870	0.08	3.7	1740	1820	26	20	9	3	5.2	6.8	18	0.01
KL32-11	227.3	230.4	0.0309		309	0.04	3.8	3540	2970	40	28	8	0.01	4.3	4.3	23	0.01
KL32-11	230.4	233.3	0.0335		335	0.05	4	2750	2770	38	36	6	0.01	4.8	4.5	22	0.01
KL32-11	233.3	235.8	0.0125		125	0.02	3.7	2640	3640	23	17	7	0.01	5.6	7.8	22	0.01
KL32-11	235.8	237.7	0.0072		72	0.04	3.4	1400	1590	26	10	7	0.01	3.6	4.0	22	0.01
KL32-11	237.7	239.7	0.0106		106	0.02	3.6	1690	860	34	24	9	3	6.1	6.8	14	0.01
KL32-11	239.7	242	0.083		830	0.08	11.5	13800	20700	14	17	6	3	13.4	18.0	27	0.1
KL32-11	242	244.5	0.0079		79	0.03	1.5	1020	356	12	14	4	0.01	3.2	2.8	9	0.01
KL32-11	244.5	245.7	0.0088		88	0.03	1.9	3950	1420	13	13	14	0.01	2.2	4.5	8	0.01
KL32-11	245.7	247.8	0.079		790	0.13	54	30000	11900	95	40	160	9	18	70.8	16	0.16
KL32-11	247.8	250.9	0.63		6300	0.78	16.1	3510	1570	41	44	69	18	4.4	15.5	19	0.01
KL32-11	250.9	254	0.029		290	0.06	3.4	4400	1410	29	17	5	0.01	8	6.8	17	0.11
KL32-11	254	255	0.021		210	0.08	2.2	2730	750	29	11	5	3	5.7	6.3	13	0.14
KL32-11	255	257.4	0.0235		235	0.1	3.3	2140	880	23	23	7	3	6	7.3	11	0.01
KL32-11	257.4	260.4	0.0136		136	0.04	5.5	5900	1900	17	17	16	0.01	6.5	4.3	9	0.14
KL32-11	260.4	262.9	0.011		110	0.02	1.8	1550	500	8	8	4	3	1.7	4.5	13	0.01
KL32-11	262.9	266	0.053		530	0.09	2.7	1430	760	15	21	7	3	2.5	10.0	15	0.01
KL32-11	266	269	0.0286		286	0.04	11.2	5900	2100	30	11	41	3	6.3	16.1	18	0.01
KL32-11	269	271.2	0.0095		95	0.03	3.2	2930	1030	9	11	7	0.01	2.7	7.0	13	0.1
KL32-11	271.2	272.7	0.008		80	0.01	2.9	2590	820	13	13	8	0.01	2.6	8.0	13	0.1
KL32-11	272.7	275.7	0.0104		104	0.03	2.1	1270	590	18	12	4	4	2.1	3.8	16	0.01
KL32-11	275.7	278.7	0.0291		291	0.03	1.1	1250	306	17	8	2	3	1.5	3.5	19	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL32-11	278.7	281.7	0.0145	145	0.01	0.9	840	252	15	14	1	3	1.2	4.3	25	0.01
KL32-11	281.7	284.7	0.0151	151	0.01	0.6	427	153	20	5	2	3	0.8	2.5	18	0.01
KL32-11	284.7	287.7	0.0174	174	0.03	1.2	1330	130	16	9	3	3	2.1	4.5	16	0.01
KL32-11	287.7	290	0.99	9900	1.28	4.3	960	61	11	47	2	17	0.4	11.5	45	0.01
KL32-11	290	293.1	0.082	820	0.11	7.6	9800	3200	190	8	6	9	36.5	15.8	21	0.44
KL32-11	293.1	296.2	0.0367	367	0.05	1.9	4050	620	63	7	2	7	5.6	12.3	27	0.1
KL32-11	296.2	298.1	0.0174	174	0.03	0.8	1120	140	15	8	3	4	1.7	2.3	15	0.01
KL32-11	298.1	300.4	0.0307	307	0.05	1.4	4810	275	49	10	3	4	3.3	6.5	17	0.01
KL32-11	300.4	302.4	0.48	4800	0.48	1.6	6700	58	51	11	2	27	4	14.5	50	0.01
KL32-11	302.4	305.5	0.94	9400	1.24	5	2400	99	72	32	2	14	7.8	19.0	20	0.01
KL32-11	305.5	308.6	0.91	9100	0.93	5.3	6700	106	35	47	2	19	2.3	16.5	30	0.01
KL32-11	308.6	311.3	0.478	4780	0.6	1.3	680	43	20	124	0.01	14	1.8	7.5	21	0.01
KL32-11	311.3	313.8	0.165	1650	0.24	1.2	1460	175	29	71	1	17	5.8	6.5	36	0.01
KL32-11	313.8	316.9	0.134	1340	0.24	0.8	205	29	20	451	2	10	0.8	4.5	17	0.01
KL32-11	316.9	318.8	0.3	3000	0.43	1.5	144	25	21	540	2	13	2.7	7.8	28	0.01
KL32-11	318.8	320.7	0.424	4240	0.35	1.6	204	55	30	387	1	16	4.5	9.0	20	0.01
KL32-11	320.7	322.4	0.425	4250	0.07	0.9	920	35	21	140	0.01	31	1.4	7.8	19	0.01
KL32-11	322.4	323.7	1.52	15200	0.95	4	7000	19	28	96	0.01	134	0.7	14.0	25	0.01
KL32-11	323.7	326.7	0.52	5200	0.47	2.8	1520	28	31	81	1	36	1.6	7.3	26	0.01
KL32-11	326.7	329.7	0.78	7800	0.52	2.3	4700	18	23	183	1	57	1.8	9.8	47	0.01
KL32-11	329.7	331.9	0.62	6200	0.5	2.9	790	26	18	17	0.01	35	0.7	4.5	37	0.01
KL32-11	331.9	334	0.451	4510	0.36	3.4	760	68	31	201	1	25	1.5	2.8	40	0.01
KL32-11	334	335.7	0.364	3640	0.56	3.5	850	500	38	680	4	23	1	9.3	17	0.01
KL32-11	335.7	338.2	0.26	2600	0.28	3.1	700	170	32	38	3	21	1	3.4	50	0.01
KL32-11	338.2	341.3	0.22	2200	0.1	0.8	102	36	2	58	0.01	8	0.2	4.0	60	0.01
KL32-11	341.3	344.1	0.46	4600	0.33	3.8	10200	186	30	8	7	31	1.3	14.8	21	0.01
KL32-11	344.1	346.3	0.35	3500	0.23	4.4	15800	305	39	7	4	35	2.5	15.5	38	0.01
KL32-11	346.3	347.7	0.38	3800	0.2	4.5	5400	640	51	40	8	16	1.4	4.3	11	0.01
KL32-11	347.7	350.2	0.211	2110	0.19	2.3	3240	70	70	6	2	16	5.3	3.8	23	0.01
KL32-11	350.2	353.2	0.298	2980	0.39	1.7	3810	65	48	36	1	32	7.3	10.8	31	0.01
KL32-11	353.2	356.3	0.88	8800	1.98	3.3	2080	570	15	114	3	48	4.3	12.5	42	0.01
KL32-11	356.3	358.4	0.27	2700	0.74	1.4	2250	1240	30	19	2	9	2.8	10.8	27	0.01
KL32-11	358.4	359.7	1.03	10300	1.67	2.8	128	37	18	27	2	12	0.6	9.0	43	0.01
KL32-11	359.7	362.7	0.54	5400	0.87	2.1	410	60	22	68	6	41	0.4	20.5	27	0.01
KL32-11	362.7	365.7	0.334	3340	0.37	0.9	106	38	14	125	1	6	0.3	4.0	91	0.01
KL32-11	365.7	368.7	1.25	12500	1.12	2.8	440	26	24	76	0.01	22	0.5	6.7	21	0.01
KL32-11	368.7	371.7	0.457	4570	0.68	0.9	269	24	14	15	2	15	0.4	5.5	13	0.01
KL32-11	371.7	374.7	3.81	38100	2.08	10.8	440	30	2	521	1	33	0.6	25.0	54	0.01
KL32-11	374.7	377.7	1.15	11500	1.98	8.5	23700	94	41	23	9	29	2	17.5	41	0.01
KL32-11	377.7	380.7	2.07	20700	1.92	13	4000	100	77	9	6	32	5.3	16.0	58	0.01
KL32-11	380.7	383.7	0.97	9700	1.75	4.6	2400	21	42	27	26	23	0.5	22.0	30	0.01
KL32-11	383.7	386.7	2.68	26800	2.25	23.1	5300	23	26	58	2	30	0.7	20.0	46	0.01
KL32-11	386.7	389.7	3.81	38100	1.87	5.3	395	22	1	13	1	30	0.6	17.5	25	0.01
KL32-11	389.7	392.7	1.78	17800	1.23	3.9	4500	12	15	20	0.01	38	0.2	19.0	36	0.01
KL32-11	392.7	395.1	1.66	16600	1.25	3.8	249	36	3	128	0.01	17	0.8	10.0	75	0.01
KL32-11	395.1	397.4	0.474	4740	1.07	6	1380	101	29	19	5	21	1.5	8.0	25	0.01
KL32-11	397.4	398.7	0.69	6900	0.46	2.4	217	47	2	67	0.01	9	0.01	8.0	68	0.01
KL32-11	398.7	401.7	0.398	3980	0.31	2.5	1460	133	12	28	1	8	1.2	8.3	64	0.01
KL32-11	401.7	404.7	0.501	5010	0.33	1.8	400	139	2	19	0.01	8	0.3	5.8	72	0.01
KL32-11	404.7	407.7	1.39	13900	1.24	2.9	760	41	8	56	1	12	0.01	10.5	52	0.01
KL32-11	407.7	410.7	0.74	7400	0.35	1.6	101	38	2	38	0.01	9	0.2	5.0	84	0.01
KL32-11	410.7	413.7	0.75	7500	0.37	3.3	900	134	18	61	2	15	2.5	7.3	102	0.01
KL32-11	413.7	416.7	1.03	10300	0.43	2.5	225	88	1	18	1	10	0.01	7.5	83	0.01
KL32-11	416.7	419.7	0.97	9700	0.36	2.8	232	178	1	17	1	9	0.01	5.5	80	0.01
KL32-11	419.7	422.7	0.461	4610	0.18	1.1	336	430	0.01	16	0.01	6	0.3	4.5	77	0.01
KL32-11	422.7	425.7	0.56	5600	0.25	1	320	290	2	19	2	6	1.2	5.3	83	0.01
KL32-11	425.7	428.7	0.69	6900	0.35	2.2	970	1380	6	21	0.01	5	0.9	5.8	77	0.01
KL32-11	428.7	431.7	0.45	4500	0.34	4.1	3410	4840	3	18	1	6	3.3	5.3	73	0.01
KL32-11	431.7	434.7	0.92	9200	0.6	1.5	78	27	3	9	0.01	7	0.01	6.3	86	0.01
KL32-11	434.7	437.7	0.63	6300	0.32	1.2	70	18	1	40	0.01	9	0.01	4.0	72	0.01
KL32-11	437.7	440.7	0.364	3640	0.16	0.9	49	17	1	25	0.01	6	0.01	2.5	69	0.01
KL32-11	440.7	443.7	0.76	7600	0.41	1.6	78	19	1	64	0.01	10	0.01	2.0	72	0.01
KL32-11	443.7	446.7	0.336	3360	0.25	0.8	50	6	1	8	0.01	7	0.01	2.3	73	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL32-11	446.7	449.7	0.62	6200	0.28	1.7	240	271	3	16	4	6	2	4.8	88	0.01
KL32-11	449.7	452.7	0.463	4630	0.28	1	81	16	4	48	0.01	7	0.4	4.0	102	0.01
KL32-11	452.7	455.7	0.473	4730	0.23	1.3	242	49	4	47	0.01	8	0.8	4.3	119	0.01
KL32-11	455.7	458.7	0.501	5010	0.32	1	88	7	1	12	0.01	8	0.01	1.3	88	0.01
KL32-11	458.7	461.7	0.75	7500	0.37	1.6	910	39	13	10	0.01	10	0.9	6.0	72	0.01
KL32-11	461.7	463.9	0.471	4710	0.32	1.4	500	150	13	15	0.01	10	1.8	5.0	71	0.01
KL32-11	463.9	467	0.74	7400	0.83	14.7	2030	1300	33	45	42	15	4	14.8	40	0.01
KL32-11	467	470.1	0.412	4120	0.3	3.2	640	295	7	43	6	9	1	6.0	56	0.01
KL32-11	470.1	473.2	0.52	5200	0.34	3	17500	59	55	4	0.01	60	7.6	26.7	34	0.01
KL32-11	473.2	475.3	0.76	7600	0.52	1.2	136	23	2	32	0.01	10	0.2	5.2	58	0.01
KL32-11	475.3	476.7	0.54	5400	0.41	1.7	680	138	9	17	2	10	1.6	7.7	59	0.01
KL34-01	0	6	0.0021	21	0.05	0.5	247	76	11	1	0.01	1	0.4	1.5	19	0.01
KL34-01	6	9	0.0011	11	0.04	0.5	206	71	11	2	0.01	1	0.6	1.7	19	0.01
KL34-01	9	12	0.0015	15	0.01	0.1	114	65	12	1	0.01	1	0.4	1.7	18	0.01
KL34-01	12	15	0.0032	32	0.02	0.1	211	80	10	3	0.01	1	0.7	1.0	17	0.01
KL34-01	15	18	0.0033	33	0.05	1.2	1400	256	14	3	0.01	1	1.3	1.5	19	0.1
KL34-01	18	21	0.0018	18	0.02	0.6	128	109	15	2	0.01	1	1	1.9	12	0.01
KL34-01	21	24	0.0016	16	0.01	0.1	84	58	12	1	0.01	1	0.4	1.8	13	0.01
KL34-01	24	27	0.001	10	0.01	0.7	169	100	20	2	0.01	1	0.4	1.8	17	0.01
KL34-01	27	30	0.0018	18	0.01	1.3	283	258	16	1	0.01	1	1.2	1.5	16	0.01
KL34-01	30	33	0.0043	43	0.01	0.5	162	62	14	3	0.01	1	0.9	1.4	19	0.01
KL34-01	33	36	0.0031	31	0.05	1.2	180	64	11	2	0.01	1	0.6	1.6	20	0.01
KL34-01	36	39	0.0014	14	0.1	0.5	144	105	13	2	0.01	1	0.3	0.7	21	0.01
KL34-01	39	42	0.0023	23	0.78	0.1	40	45	27	1	0.01	1	0.7	1.2	24	0.01
KL34-01	42	45	0.0009	9	0.17	0.1	57	36	15	2	0.01	1	0.3	1.2	23	0.01
KL34-01	45	48	0.0008	8	0.63	0.1	108	53	13	1	0.01	1	0.6	1.1	19	0.01
KL34-01	48	53	0.0016	16	0.2	0.6	333	182	11	1	0.01	1	0.6	2.6	17	0.01
KL34-01	53	56	0.0009	9	0.14	0.1	54	25	15	3	0.01	1	1	1.3	22	0.01
KL34-01	56	59	0.003	30	0.29	0.1	18	21	14	3	0.01	1	0.4	1.2	22	0.01
KL34-01	59	62	0.0012	12	0.29	0.1	29	26	17	2	0.01	1	0.5	1.3	21	0.01
KL34-01	62	65	0.0015	15	0.1	0.1	31	20	14	1	0.01	1	0.7	2.6	19	0.01
KL34-01	65	68	0.0116	116	0.12	4.8	292	218	46	3	0.01	1	4.2	3.7	14	0.01
KL34-01	68	71	0.0261	261	0.14	22.5	10400	7800	130	8	14	1	16	83.0	21	0.21
KL34-01	71	74	0.0053	53	0.89	3	870	265	96	3	0.01	1	12.5	8.4	28	0.19
KL34-01	74	77	0.0047	47	0.59	0.1	172	25	8	1	0.01	1	0.7	5.3	14	0.01
KL34-01	77	81	0.0027	27	0.62	0.1	139	42	11	1	0.01	1	1.3	6.3	18	0.01
KL34-01	81	84	0.0024	24	0.37	0.9	27	20	19	3	0.01	1	1.2	3.0	28	0.01
KL34-01	84	87	0.004	40	0.08	0.1	19	12	13	1	0.01	1	0.4	0.8	26	0.01
KL34-01	87	90	0.0013	13	0.04	0.1	20	13	14	1	0.01	1	0.2	1.4	25	0.01
KL34-01	90	93	0.0353	353	0.03	0.1	16	11	8	1	0.01	1	0.01	1.6	20	0.01
KL34-01	93	96	0.0029	29	0.01	0.1	23	12	9	1	0.01	1	0.01	1.4	25	0.01
KL34-01	96	99	0.0028	28	0.01	0.1	40	24	6	1	0.01	1	0.01	1.2	23	0.01
KL34-01	99	102	0.0024	24	0.01	0.1	34	25	10	1	0.01	1	0.4	1.8	20	0.01
KL34-01	102	105	0.0028	28	0.13	0.1	56	45	36	1	0.01	1	1	2.1	19	0.01
KL34-01	105	108	0.0039	39	0.05	1.6	440	305	50	31	9	2	3.1	4.8	28	0.01
KL34-01	108	111	0.004	40	0.03	1.5	268	351	42	3	2	2	2.8	2.7	42	0.01
KL34-01	111	114	0.0065	65	0.09	0.8	450	217	65	5	1	3	3	3.8	99	0.01
KL34-01	114	117	0.0093	93	0.02	3	129	261	25	3	7	3	1.7	7.5	135	0.01
KL34-01	117	124.3	0.097	970	0.4	38	11900	8600	260	46	150	1	58	18.0	69	0.97
KL34-01	124.3	127.5	0.25	2500	1.44	201	66200	70900	610	20	610	3	160	48.0	72	2.95
KL34-01	127.5	132	0.138	1380	0.83	45	30000	13800	460	38	100	14	156	43.0	74	0.98
KL34-01	132	136.5	0.0081	81	0.05	2.9	1110	560	29	12	7	3	4	3.2	221	0.1
KL34-01	136.5	142.5	0.0147	147	0.09	1.4	850	322	74	12	3	2	2.8	2.4	31	0.01
KL34-01	142.5	145.2	0.018	180	0.08	0.8	1700	210	120	15	3	3	5.8	2.1	131	0.01
KL34-01	145.2	147.5	0.0038	38	0.48	1.1	5200	1470	180	76	1	1	13	5.5	64	0.21
KL34-01	147.5	150.5	0.0101	101	0.46	0.9	5200	1400	180	351	3	1	10.1	4.5	50	0.19
KL34-01	150.5	153	0.0204	204	0.43	2.5	2250	500	260	90	11	2	9.3	6.0	113	0.11
KL34-01	153	155.5	0.0248	248	0.4	4.9	8100	1180	180	256	24	4	14	11.5	59	0.41
KL34-01	155.5	158	2.86	28600	0.78	49	17000	3000	5750	62	190	160	625	61.3	44	1.1
KL34-01	158	161	0.4	4000	0.2	9.5	34600	1040	770	530	40	30	60	43.8	40	0.18
KL34-01	161	164	0.0114	114	0.15	2.4	1400	620	40	21	4	1	8	8.8	20	0.1
KL34-01	164	166.4	0.0178	178	0.09	2.6	770	570	24	13	6	1	8.8	6.4	21	0.1
KL34-01	166.4	169	0.0133	133	0.3	2.6	1360	520	35	47	4	1	5.4	11.3	18	0.14

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL34-01	169	172	0.0231		231	0.18	8.2	1970	1420	76	95	17	1	25	26.3	20	0.1
KL34-01	172	175	0.06		600	0.4	43	8600	7800	120	153	14	3	75	22.5	35	0.44
KL34-01	175	178	0.0054		54	0.07	4	880	670	18	48	9	1	6.9	6.5	24	0.01
KL34-01	178	181	0.0037		37	0.06	1.7	430	254	14	31	5	1	2.8	3.9	25	0.01
KL34-01	181	184	0.014		140	0.12	4.7	790	630	29	79	13	1	16.2	11.0	32	0.1
KL34-01	184	187	0.0407		407	0.2	8.3	4900	2100	100	114	17	1	13.4	15.5	28	0.13
KL34-01	187	190	0.047		470	0.28	12.3	5800	2700	110	116	27	7	13.4	23.3	31	0.16
KL34-01	190	193	0.0205		205	0.24	5.8	2200	2100	90	57	12	3	12	11.6	20	0.1
KL34-01	193	196	0.0163		163	0.21	6.2	1640	2400	53	57	12	1	9.6	13.9	16	0.01
KL34-01	196	199	0.0067		67	0.08	4.3	1140	1310	29	55	10	1	3.4	7.8	32	0.01
KL34-01	199	202	0.0072		72	0.05	3.7	1240	1000	22	40	6	1	4.5	6.0	13	0.01
KL34-01	202	205	0.0045		45	0.03	2.3	670	570	19	45	5	1	2.4	3.8	12	0.01
KL34-01	205	208	0.0063		63	0.07	2.9	780	510	21	35	5	1	3.2	5.3	20	0.01
KL34-01	208	211	0.0148		148	0.14	6.3	3600	2300	56	53	10	1	6.4	12.0	13	0.1
KL34-01	211	213.3	0.0268		268	0.15	6.6	4300	2800	89	88	12	1	6.8	17.6	12	0.1
KL34-01	213.3	217.4	3.62		36200	1.7	118	99000	69000	1690	578	267	17	350	84.0	172	0.25
KL34-01	217.4	223.8	1.16		11600	0.9	11.7	21300	650	1420	61	236	22	105	110.0	280	0.14
KL34-01	223.8	227	0.41		4100	0.58	55	54000	36400	1310	385	54	9	132	131.0	48	0.58
KL34-01	227	230	0.4		4000	2.3	30.9	25600	9000	700	470	62	23	51	70.5	53	0.66
KL34-01	230	233	0.051		510	0.94	4.3	2300	800	160	87	12	5	7.3	16.0	25	0.19
KL34-01	233	236	0.2		2000	0.97	35.3	12900	18600	150	270	35	9	32	57.0	50	0.19
KL34-01	236	239	0.28		2800	1.13	60	28700	38800	220	271	32	12	80	61.0	68	0.55
KL34-01	239	241	0.079		790	0.55	58	9800	10500	150	200	11	4	101	21.5	34	0.51
KL34-01	241	243	0.117		1170	0.47	48	5800	9000	170	89	13	8	66	20.3	22	0.28
KL34-01	243	246	0.25		2500	0.57	39.7	17200	10500	310	336	27	26	42	47.5	41	0.22
KL34-01	246	249.7	0.12		1200	0.21	16.9	9500	7100	200	520	35	9	18.5	37.0	28	0.12
KL34-01	249.7	253	0.0108		108	0.12	4.7	1530	1700	72	65	5	1	3.7	4.3	18	0.1
KL34-01	253	256	0.0031		31	0.1	1.4	235	313	19	16	4	1	1	2.3	19	0.01
KL34-01	256	259	0.024		240	0.4	6.5	3100	1560	65	60	7	1	16	9.9	31	0.17
KL34-01	259	262	0.0137		137	0.26	3.3	1200	590	56	36	7	1	9.5	4.1	24	0.01
KL34-01	262	265	0.012		120	0.17	1.5	590	243	54	48	3	1	6.4	3.6	30	0.01
KL34-01	265	268	0.0147		147	0.12	4.1	4700	3000	58	23	6	1	6.6	4.5	23	0.01
KL34-01	268	271	0.0067		67	0.05	1	820	580	29	23	2	1	2.4	2.2	17	0.01
KL34-01	271	274	0.0077		77	0.13	1.5	900	400	54	31	2	1	2.4	7.4	18	0.01
KL34-01	274	277	0.003		30	0.05	1.5	382	1420	14	42	0.01	1	2	32.5	16	0.01
KL34-01	277	280	0.0122		122	0.08	1.8	1320	720	32	32	3	1	3.2	12.1	16	0.01
KL34-01	280	283	0.0092		92	0.03	0.8	1030	400	13	15	1	1	0.8	7.6	12	0.01
KL34-01	283	286	0.0133		133	0.14	1.5	3780	1500	30	23	3	2	3.6	16.6	20	0.01
KL34-01	286	289	0.0022		22	0.04	0.5	260	301	7	9	1	1	1.1	3.2	17	0.01
KL34-01	289	292	0.0082		82	0.15	3.4	610	3400	30	35	3	1	8.3	15.5	19	0.01
KL34-01	292	295	0.009		90	0.17	4.4	760	4100	38	36	3	1	8.2	23.5	16	0.01
KL34-01	295	298	0.013		130	0.09	1.8	530	387	39	143	5	2	3	6.6	19	0.01
KL34-01	298	301	0.0026		26	0.21	0.9	347	414	13	15	2	1	1.4	4.3	17	0.01
KL34-01	301	304	0.003		30	0.07	0.5	229	147	13	11	1	1	0.9	2.1	19	0.01
KL34-01	304	307	0.0072		72	0.17	3.6	2200	2400	36	20	2	1	4.2	10.3	19	0.01
KL34-01	307	310	0.0084		84	0.16	4.9	2680	3100	49	21	2	1	6.6	14.3	17	0.01
KL34-01	310	313	0.0054		54	0.16	1.9	610	1170	25	23	2	1	5.4	10.0	16	0.01
KL34-01	313	316	0.0187		187	0.16	2.3	2350	910	52	24	5	3	4	10.1	17	0.01
KL34-01	316	319	0.024		240	0.19	4	3310	1530	66	26	7	2	6.8	11.3	18	0.01
KL34-01	319	322	0.0202		202	0.14	1.9	1000	440	65	82	3	4	7.6	3.5	27	0.01
KL34-01	322	325	0.056		560	0.12	5.6	4170	3100	160	165	9	4	22	8.1	19	0.01
KL34-01	325	328	0.047		470	0.16	3.3	4280	1350	64	163	9	6	6.1	9.1	19	0.01
KL34-01	328	331	0.22		2200	0.18	6.5	2250	1350	200	193	14	8	4.9	10.1	18	0.01
KL34-01	331	334	0.064		640	0.12	6.7	3250	840	33	420	32	6	2.6	42.0	23	0.01
KL34-01	334	337	0.096		960	0.09	10.8	10200	1370	30	280	37	7	2.2	48.0	34	0.01
KL34-01	337	340	0.0164		164	0.04	2.4	1760	381	23	84	8	3	1	19.8	30	0.01
KL34-01	340	343	0.057		570	0.1	2.9	1510	1560	73	42	12	4	12.8	27.0	17	0.01
KL34-01	343	346	0.093		930	0.16	7.1	1520	2400	140	60	18	4	28	16.5	17	0.01
KL34-01	346	349	0.117		1170	0.06	24.6	2570	2350	69	94	99	3	3.9	43.0	21	0.01
KL34-01	349	352	0.071		710	0.08	5.8	3070	1400	59	540	40	5	5.8	9.0	23	0.01
KL34-01	352	355	0.0219		219	0.11	1.3	750	362	43	24	5	4	4.4	5.0	23	0.01
KL34-01	355	358	0.08		800	0.1	4.6	1840	1700	79	54	11	3	17.5	14.5	18	0.01
KL34-01	358	361	0.0224		224	0.11	2.3	1480	420	58	16	13	4	2.2	10.6	20	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL34-01	361	364	0.0275		275	0.09	2.2	1840	650	61	18	8	3	1.9	16.1	18	0.01
KL34-01	364	367	0.0249		249	0.15	1	1000	311	46	14	2	2	2.4	9.6	20	0.01
KL34-01	367	370	0.0241		241	0.06	1.1	1140	550	33	11	1	3	1.9	5.1	23	0.01
KL34-01	370	373	0.052		520	0.27	5.2	2380	1380	54	21	2	3	3.2	10.2	30	0.01
KL34-01	373	376	0.071		710	0.23	6.4	3160	1280	110	296	35	7	4.9	13.6	25	0.01
KL34-01	376	379	0.0288		288	0.16	1.2	1170	415	110	10	2	10	3.8	4.2	36	0.01
KL34-01	379	382	0.061		610	0.35	4.2	3740	2140	210	22	4	6	13.5	8.5	30	0.01
KL34-01	382	385	0.053		530	0.1	1.9	1060	391	50	118	9	6	3.6	14.5	31	0.01
KL34-01	385	388	0.0308		308	0.04	1.2	400	245	24	44	7	5	0.3	10.0	26	0.01
KL34-01	388	391	0.083		830	0.04	3.5	920	640	35	357	25	8	2.5	16.0	24	0.01
KL34-01	391	394	0.079		790	0.06	3.7	1270	1160	50	384	16	7	4.5	16.5	23	0.01
KL34-01	394	397	0.03		300	0.07	1.6	1130	376	45	264	8	4	1.9	10.0	22	0.01
KL34-01	397	400	0.0165		165	0.07	0.8	386	201	75	51	3	2	3.6	11.3	28	0.01
KL34-01	400	403	0.0161		161	0.2	1.2	430	245	92	49	3	1	8.5	16.5	32	0.01
KL34-01	403	406	0.076		760	0.15	13.2	1530	1450	61	56	56	2	8	37.0	20	0.01
KL34-01	406	409	0.0408		408	0.04	1	403	155	30	153	20	4	0.9	8.8	22	0.01
KL34-01	409	412	0.0139		139	0.03	0.1	291	71	28	10	0.01	2	0.7	1.6	19	0.01
KL34-01	412	415	0.081		810	0.82	15.3	1870	110	140	94	2	5	9.9	4.6	39	0.01
KL34-01	415	418	0.0077		77	0.18	18.4	185	54	78	6	0.01	3	10.1	2.5	22	0.01
KL34-01	418	421	0.0096		96	0.06	0.1	201	78	61	7	0.01	3	2	1.6	19	0.01
KL34-01	421	424	0.0047		47	0.03	5.2	620	314	45	1	0.01	1	3.3	2.3	14	0.01
KL34-01	424	427	0.0064		64	0.04	0.1	41	25	31	1	0.01	1	0.5	0.9	16	0.01
KL34-01	427	430	0.0032		32	0.04	0.1	86	34	47	3	0.01	1	0.8	1.0	14	0.01
KL34-01	430	433	0.0033		33	0.04	0.8	59	57	50	3	0.01	1	1.3	1.3	15	0.01
KL34-01	433	436	0.0091		91	0.05	12	960	630	51	1	0.01	1	8.1	5.9	18	0.01
KL34-01	436	439	0.0126		126	0.05	20.5	1780	1040	50	1	0.01	1	12.1	11.2	14	0.01
KL34-01	439	442	0.0025		25	0.05	0.1	41	24	72	3	0.01	1	1.8	1.2	14	0.01
KL34-01	442	445	0.0022		22	0.05	0.1	46	27	57	7	0.01	1	1.2	1.3	14	0.01
KL34-01	445	448	0.0025		25	0.03	0.1	30	30	43	6	0.01	1	0.8	1.2	14	0.01
KL34-01	448	451	0.0083		83	0.03	0.7	113	61	60	7	1	1	2.5	2.0	13	0.01
KL34-01	451	454	0.0097		97	0.04	0.5	100	54	63	9	1	1	3.3	2.1	15	0.01
KL34-01	454	457	0.0094		94	0.02	0.1	82	65	61	6	3	1	1.5	1.9	17	0.01
KL34-01	457	460	0.0066		66	0.03	0.1	69	47	75	9	1	1	2.6	1.9	16	0.01
KL34-01	460	463	0.0041		41	0.01	0.1	78	30	21	3	0.01	1	0.7	1.0	16	0.01
KL34-01	463	466	0.0097		97	0.02	0.1	267	130	43	4	3	1	0.6	1.1	16	0.01
KL34-01	466	469	0.0027		27	0.01	0.1	60	21	20	6	0.01	2	0.4	0.9	17	0.01
KL34-01	469	472	0.0366		366	0.07	3	570	480	41	12	14	1	3.4	12.1	19	0.01
KL34-01	472	475	0.0288		288	0.01	0.1	54	21	30	12	1	1	0.6	1.1	17	0.01
KL34-01	475	478	0.0036		36	0.01	0.1	56	20	12	5	0.01	1	0.4	0.9	16	0.01
KL34-01	478	481	0.004		40	0.01	0.1	41	21	19	7	0.01	1	0.4	0.8	17	0.01
KL34-01	481	484	0.0035		35	0.01	0.1	82	27	20	6	0.01	1	0.4	1.0	17	0.01
KL34-01	484	487	0.0047		47	0.02	0.1	32	15	27	80	0.01	1	0.4	1.1	16	0.01
KL34-01	487	490	0.0031		31	0.02	0.1	28	26	31	8	0.01	1	0.7	0.8	17	0.01
KL34-01	490	493	0.0045		45	0.01	0.1	36	20	26	5	0.01	2	0.6	0.8	15	0.01
KL34-01	493	496	0.0027		27	0.01	0.1	33	21	20	4	0.01	2	0.4	1.0	13	0.01
KL34-01	496	499	0.005		50	0.02	0.1	38	14	29	124	0.01	3	0.5	1.3	16	0.01
KL34-01	499	502	0.053		530	0.04	0.1	81	25	58	18	2	6	0.7	1.3	17	0.01
KL34-01	502	505	0.0153		153	0.07	0.1	100	18	94	15	2	3	1.5	1.5	25	0.01
KL34-01	505	508	0.0225		225	0.06	1.5	1200	1170	57	14	3	3	2	3.1	20	0.01
KL34-01	508	511	0.0207		207	0.06	2.1	1440	1130	61	6	5	4	2.6	5.1	19	0.01
KL34-01	511	514	0.0068		68	0.01	0.1	53	22	53	7	2	2	0.7	0.8	18	0.01
KL34-01	514	517	0.0198		198	0.04	0.1	160	23	58	24	6	6	0.9	2.2	22	0.01
KL34-01	517	520	0.0203		203	0.07	0.1	181	23	90	23	6	9	1	1.8	20	0.01
KL34-01	520	523	0.0201		201	0.43	0.8	132	34	270	18	3	7	17.3	3.8	50	0.01
KL34-01	523	526	0.0133		133	0.04	0.1	68	20	65	8	1	1	2.7	1.0	24	0.01
KL34-01	526	529	0.0408		408	0.15	0.6	840	31	130	29	3	3	4.7	2.1	37	0.01
KL34-01	529	532	0.0193		193	0.04	0.1	780	28	33	17	3	2	0.5	1.0	21	0.01
KL34-01	532	535	0.05		500	0.03	0.1	190	37	42	27	9	2	0.5	1.4	24	0.01
KL34-01	535	538	0.0142		142	0.01	0.1	50	34	18	13	2	3	0.2	0.8	25	0.01
KL34-01	538	541	0.0033		33	0.01	0.1	44	17	11	5	0.01	1	0.5	0.8	19	0.01
KL34-01	541	544	0.0032		32	0.01	0.1	520	18	19	11	0.01	1	0.8	0.8	17	0.01
KL34-01	544	547	0.0235		235	0.05	0.1	2190	68	110	11	1	2	4.1	2.1	23	0.01
KL34-01	547	550	0.013		130	0.06	0.1	297	30	70	14	2	1	1.6	1.8	19	0.01

Hole	From	To	Cu	Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL34-01	550	553	0.0241	241	0.06	0.1	2420	81	93	12	2	1	2.4	1.4	20	0.01
KL34-01	553	556	0.042	420	0.17	0.1	1510	52	110	56	7	4	1.4	2.2	35	0.01
KL34-01	556	559	0.0076	76	0.04	0.1	122	25	39	32	2	1	0.8	0.7	22	0.01
KL34-01	559	562	0.0108	108	0.13	0.1	132	26	55	40	5	2	1.4	1.7	28	0.01
KL34-01	562	565	0.0036	36	0.12	0.1	93	30	91	14	0.01	4	2.1	1.5	29	0.01
KL34-01	565	567.7	0.0113	113	0.11	0.1	108	40	90	14	0.01	2	3.3	2.2	26	0.01
KL34-02	0	6	0.041	410	0.02	0.9	247	148	35	5	4	1	5.1	2.0	49	0.01
KL34-02	6	9	0.0082	82	0.05	1.2	1000	338	27	6	0.01	1	2.9	2.0	66	0.01
KL34-02	9	13.1	0.008	80	0.04	1.2	850	304	19	3	0.01	1	2.4	1.8	42	0.01
KL34-02	13.1	15	0.0104	104	0.01	0.9	337	106	15	3	0.01	1	0.8	1.2	16	0.01
KL34-02	15	17.3	0.0176	176	0.08	1.6	640	176	26	2	0.01	1	0.9	1.0	23	0.01
KL34-02	17.3	20.3	0.0092	92	0.04	1.2	1880	460	28	4	0.01	1	1.4	1.3	22	0.01
KL34-02	20.3	23.3	0.012	120	0.1	3.2	3250	1510	34	4	0.01	1	3.2	2.0	26	0.1
KL34-02	23.3	26.3	0.0085	85	0.19	7	9000	3800	25	1	0.01	1	5.8	1.8	19	0.59
KL34-02	26.3	29.3	0.0114	114	0.23	9	15800	6000	26	2	0.01	1	5.1	1.8	20	0.26
KL34-02	29.3	32.3	0.0072	72	0.01	1	500	610	9	1	0.01	1	1.3	1.3	25	0.16
KL34-02	32.3	34.5	0.0259	259	0.03	5.7	2125	3750	38	4	2	1	4.8	17.1	39	0.22
KL34-02	34.5	36.8	0.022	220	0.03	17.5	6100	7200	57	4	26	2	12.5	20.4	26	0.13
KL34-02	36.8	38.5	0.76	7600	0.49	394	107000	84800	2400	12	460	34	200	337.0	174	3.4
KL34-02	38.5	41.4	0.0143	143	0.15	15	7500	7300	180	40	23	1	6.8	12.1	23	0.24
KL34-02	41.4	44.3	0.0121	121	0.01	0.1	167	93	18	1	0.01	1	1.2	1.5	48	0.01
KL34-02	44.3	47.3	0.0073	73	0.02	0.1	186	103	12	1	0.01	1	0.8	2.0	46	0.01
KL34-02	47.3	50.3	0.0085	85	0.01	0.1	102	66	11	3	1	1	1.1	2.0	30	0.01
KL34-02	50.3	53.3	0.088	880	0.01	0.1	148	92	10	7	0.01	1	1.8	1.8	40	0.01
KL34-02	53.3	56.3	0.0202	202	0.01	0.1	110	112	11	7	0.01	1	1	1.5	38	0.01
KL34-02	56.3	59.3	0.0125	125	0.03	1.4	540	213	17	3	3	1	1.3	2.8	29	0.01
KL34-02	59.3	62.3	0.0075	75	0.05	0.1	1230	362	32	3	0.01	1	2	1.8	48	0.01
KL34-02	62.3	65.3	0.051	510	0.03	0.1	710	161	17	1	2	1	2.3	1.5	60	0.01
KL34-02	65.3	68.3	0.0191	191	0.05	1	376	96	84	3	32	4	4.8	13.3	67	0.01
KL34-02	68.3	71.3	0.0038	38	0.02	0.6	152	102	22	2	4	3	0.9	11.8	61	0.01
KL34-02	71.3	74.3	0.8	8000	0.15	139	30100	8250	630	19	830	2	33	356.0	129	0.54
KL34-02	74.3	77.3	0.0149	149	0.09	4.8	2300	1180	88	13	19	1	4.5	8.0	314	0.18
KL34-02	77.3	80.3	0.053	530	0.06	3	1520	450	130	5	84	1	8.3	10.3	150	0.01
KL34-02	80.3	83.3	0.108	1080	0.16	17.8	3700	13000	250	9	60	5	21	27.2	157	0.55
KL34-02	83.3	86.3	0.067	670	0.04	9.4	1620	3210	100	5	36	1	11	6.3	317	0.14
KL34-02	86.3	89.3	0.0263	263	0.03	10.1	1820	3350	78	5	50	1	4.1	5.8	135	0.1
KL34-02	89.3	92.3	0.0155	155	0.08	3	3330	1290	50	10	10	1	4.4	3.8	233	0.3
KL34-02	92.3	94.1	0.0154	154	0.12	5	3810	1280	71	11	25	1	9.8	6.3	110	0.17
KL34-02	94.1	98.3	0.046	460	0.08	18	4400	2600	170	13	33	1	14.3	5.8	260	0.24
KL34-02	98.3	101.3	0.0048	48	0.13	1.5	1460	388	96	11	3	1	3	2.0	289	0.01
KL34-02	101.3	104.3	0.0054	54	0.14	2.5	1700	590	99	20	6	1	11	2.3	99	0.01
KL34-02	104.3	106	0.0042	42	0.17	2.9	1710	560	96	20	7	1	6.2	2.8	48	0.01
KL34-02	106	108.2	0.022	220	0.33	6.3	2320	5180	190	68	5	2	18	8.8	68	0.1
KL34-02	108.2	110.3	0.0057	57	0.04	1.8	950	720	14	10	4	1	3.8	3.8	24	0.01
KL34-02	110.3	113.3	0.0115	115	0.06	2.7	2700	1410	30	12	3	1	4.5	5.6	19	0.24
KL34-02	113.3	116.3	0.0092	92	0.07	0.7	800	364	17	12	2	1	2.9	2.0	21	0.01
KL34-02	116.3	119.3	0.003	30	0.05	0.8	371	254	9	4	2	1	0.6	2.0	18	0.01
KL34-02	119.3	121.8	0.0034	34	0.05	4.5	740	580	9	4	19	1	1.3	3.5	18	0.01
KL34-02	123.3	125.3	0.0038	38	0.07	2.2	287	290	12	7	7	1	1.2	4.0	21	0.01
KL34-02	123.3	125.3	0.071	710	0.2	44	18500	3700	66	15	334	2	16.8	26.2	24	0.12
KL34-02	125.3	128.3	0.0113	113	0.3	2.7	2020	530	48	25	9	1	5.7	4.8	35	0.01
KL34-02	128.3	131.3	0.094	940	0.35	5	1500	480	210	212	30	9	6.4	14.0	22	0.01
KL34-02	131.3	134.5	0.0084	84	0.21	2.7	1280	630	37	55	8	1	1.8	5.5	23	0.01
KL34-02	134.5	137.3	0.0073	73	0.06	3.4	1300	1360	26	21	6	1	2.3	4.5	26	0.01
KL34-02	137.3	140.2	0.0052	52	0.07	4.5	510	1700	19	46	12	1	2.4	6.5	26	0.01
KL34-02	140.2	142.7	0.0173	173	0.14	5.8	2820	1680	47	18	18	1	6.1	8.0	24	0.01
KL34-02	142.7	145.6	0.0071	71	0.12	7.7	800	1130	36	14	24	1	1.7	4.5	22	0.01
KL34-02	145.6	148.1	0.0028	28	0.07	2.2	300	440	13	18	5	1	0.9	2.8	13	0.01
KL34-02	148.1	150.9	0.0084	84	0.12	3.5	1700	1090	40	21	6	1	3.1	5.8	16	0.01
KL34-02	150.9	155.3	0.0206	206	0.25	8	2800	2300	98	138	25	2	8	8.5	40	0.01
KL34-02	155.3	158.6	0.0036	36	0.05	1.5	600	650	16	22	3	1	1.3	2.0	13	0.01
KL34-02	158.6	164.3	0.0041	41	0.07	1.7	1000	1230	24	15	1	1	3.4	2.8	13	0.01
KL34-02	164.3	167.3	0.0047	47	0.07	1.7	1870	1210	30	18	1	1	3.8	3.0	12	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL34-02	167.3	170.3	0.031		310	0.27	12.8	8200	7500	120	75	28	1	18	25.4	19	0.01
KL34-02	170.3	173.3	0.0066		66	0.08	3.5	1450	610	46	171	6	1	3.2	4.0	19	0.01
KL34-02	173.3	175.7	0.01		100	0.11	5.7	4400	3900	41	91	6	1	5.9	10.8	18	0.01
KL34-02	175.7	177.5	0.041		410	0.21	13.4	9800	6300	97	103	34	1	8.5	32.3	14	0.01
KL34-02	177.5	180.6	0.0222		222	0.08	3.1	2090	700	38	37	12	6	2.6	6.6	19	0.01
KL34-02	180.6	183.5	0.0378		378	0.25	12.9	9200	7300	110	36	23	3	12.9	14.8	17	0.14
KL34-02	183.5	186.4	0.11		1100	0.93	10.3	9200	3300	440	93	26	18	19	10.5	29	0.64
KL34-02	186.4	188.3	0.09		900	1.13	10.8	12600	2300	250	171	34	8	11	10.3	40	1.16
KL34-02	188.3	191.3	0.24		2400	0.38	20.3	24000	3500	140	440	73	5	6.6	15.8	17	1.24
KL34-02	191.3	193.2	0.103		1030	0.53	17.6	7500	3900	140	211	58	7	6	20.8	42	1.42
KL34-02	193.2	194.8	0.071		710	0.44	10.2	5900	3200	130	55	21	4	3.5	14.3	25	1.04
KL34-02	194.8	197.3	0.77		7700	1.36	38	560	9400	990	105	78	11	34	20.3	245	1.2
KL34-02	197.3	202.1	0.65		6500	1.56	17.7	690	450	1190	88	94	87	21	19.5	203	0.34
KL34-02	202.1	204.6	1.17		11700	2.43	20.8	210	141	210	90	30	55	10.5	94.0	295	0.48
KL34-02	204.6	207.4	1.83		18300	1.36	18.3	217	135	220	316	15	56	4.4	40.5	280	0.41
KL34-02	207.4	210.3	0.58		5800	0.83	7.3	387	146	120	1280	12	24	2.5	12.8	394	0.47
KL34-02	210.3	212.3	0.53		5300	0.72	6.8	205	102	110	750	27	23	2.2	21.8	176	0.21
KL34-02	212.3	215.3	0.496		4960	1.23	7.5	660	344	100	400	127	21	2.9	46.5	308	0.37
KL34-02	215.3	218.3	1.25		12500	1.75	14.1	770	227	170	147	46	24	5.8	35.0	129	0.5
KL34-02	218.3	221.3	0.91		9100	1.44	10.7	1700	410	80	417	11	22	5.2	19.5	171	0.3
KL34-02	221.3	224.3	0.66		6600	0.92	6.3	228	89	74	95	8	46	4.1	55.0	141	0.01
KL34-02	224.3	227.3	1		10000	1.38	9	98	37	36	100	5	38	3	19.0	48	0.01
KL34-02	227.3	230.3	0.89		8900	1	8.6	314	96	66	38	7	36	4.4	20.8	50	0.01
KL34-02	230.3	233.3	0.78		7800	0.51	6.1	203	125	45	123	8	26	7.5	15.0	38	0.01
KL34-02	233.3	236.3	0.68		6800	0.45	4.9	300	169	58	38	4	43	8	9.8	71	0.01
KL34-02	236.3	239.3	2.35		23500	2.04	16.8	1790	163	120	187	11	170	8.5	36.0	60	0.01
KL34-02	239.3	242.3	1.47		14700	1.57	6.8	580	187	100	310	6	72	7	38.5	246	0.24
KL34-02	242.3	245.3	0.73		7300	1.32	3.8	1250	170	86	265	5	57	3.8	42.0	150	0.25
KL34-02	245.3	249.9	0.78		7800	0.89	21.5	750	480	120	245	7	45	4.8	15.5	150	0.34
KL34-02	249.9	251.3	0.8		8000	0.96	4.7	330	91	150	100	11	73	6.8	20.8	82	0.2
KL34-02	251.3	254.3	3.11		31100	2.19	11	2200	235	140	142	5	173	2.8	28.0	251	0.61
KL34-02	254.3	257.3	1.84		18400	2.6	6.3	1200	146	83	37	4	45	1.9	20.5	86	1.31
KL34-02	257.3	260.3	1.45		14500	2.25	7	650	120	24	123	7	78	1.2	25.5	187	0.6
KL34-02	260.3	263.3	1.55		15500	2.04	6	286	47	15	328	5	74	1	19.5	171	0.67
KL34-02	263.3	266.3	2.21		22100	1.65	7.6	530	37	14	233	4	76	1.1	29.0	50	2.09
KL34-02	266.3	269.3	2.02		20200	1.76	7.5	850	24	3	50	3	49	0.6	6.8	53	0.01
KL34-02	269.3	271.4	1.73		17300	1.84	5.2	1100	57	10	90	5	82	1.6	16.0	79	0.34
KL34-02	271.4	274.5	2.52		25200	2.15	7.7	1110	106	4	85	4	87	1.3	24.0	60	0.01
KL34-02	274.5	277.6	3.02		30200	2.04	8	510	20	4	104	2	70	0.8	22.0	70	0.01
KL34-02	277.6	279.2	1.34		13400	0.92	4.8	276	21	11	84	4	21	1.5	12.0	65	0.01
KL34-02	279.2	280.8	2.65		26500	1.87	5.9	820	56	6	410	3	71	1.5	26.0	65	0.01
KL34-02	280.8	283.9	2.32		23200	2.09	6.5	700	57	28	263	3	85	1.5	35.0	124	0.01
KL34-02	283.9	287.1	2.43		24300	2.26	7.1	630	96	120	120	6	150	2.8	21.0	61	0.58
KL34-02	287.1	290.3	2.69		26900	2.11	6.1	2250	182	280	184	12	66	4.5	51.0	121	2.34
KL34-02	290.3	293.3	2.88		28800	3.06	13.2	2750	306	140	187	5	30	8.8	28.0	216	3.5
KL34-02	293.3	296.3	2.58		25800	2.67	9	550	48	47	24	4	53	3.6	28.0	153	0.36
KL34-02	296.3	299.3	2.52		25200	1.65	8.3	327	32	80	291	5	58	1.8	41.5	136	0.6
KL34-02	299.3	302.3	2.71		27100	2.73	12.3	430	35	50	196	32	50	1.4	31.0	104	0.01
KL34-02	302.3	305.3	3.45		34500	4.87	14.7	800	76	42	155	4	76	2.1	30.0	51	0.38
KL34-02	305.3	308.1	2.57		25700	4.26	8.2	19900	196	45	110	4	15	2.1	30.0	135	0.6
KL34-02	308.1	311.1	5.46		54600	3.76	14.1	1480	124	140	610	3	113	5.1	40.7	52	0.96
KL34-02	311.1	314.2	5.24		52400	2.98	8.2	1110	910	54	292	1	84	7.7	24.7	71	0.98
KL34-02	314.2	317.2	2.12		21200	1.34	4.5	870	480	21	15	3	63	3.8	13.3	56	0.36
KL34-02	317.2	320.2	2.9		29000	2.05	4.5	750	113	21	115	1	68	2.4	18.0	82	0.01
KL34-02	320.2	323.2	2.45		24500	1.89	6.4	211	80	120	467	3	70	5.2	19.0	325	0.01
KL34-02	323.2	326.3	2.81		28100	1.97	6.8	2110	430	120	134	8	60	2.6	23.0	143	0.01
KL34-02	326.3	329.3	4.23		42300	3.78	9.3	1480	242	56	56	26	58	3.7	21.0	144	0.01
KL34-02	329.3	332.3	3.18		31800	2.8	5.8	1200	203	52	50	3	75	8.3	19.0	66	0.01
KL34-02	332.3	335.3	3.21		32100	2.69	5.4	930	102	57	219	1	78	6.8	15.0	116	0.01
KL34-02	335.3	338.3	3.51		35100	3	5.7	560	158	190	94	1	71	10.8	20.0	175	0.01
KL34-02	338.3	340.4	2.38		23800	2.51	4.3	560	288	290	156	2	81	10.8	23.0	179	0.01
KL34-02	340.4	342	2.3		23000	1.96	7	780	84	110	197	6	67	2.9	37.5	133	0.01
KL34-02	342	344.3	1.78		17800	2.78	4.6	780	420	140	122	2	57	6.8	15.0	128	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL34-02	344.3	347.3	2	20000	2.1	5.2	1210	600	86	940	6	53	6	14.0	129	0.01
KL34-02	347.3	350.3	1.93	19300	1.43	5.3	720	2700	87	650	4	44	6.9	12.0	150	0.01
KL34-02	350.3	353.3	1.94	19400	1.48	4.7	560	430	100	365	7	54	3.1	17.3	158	0.01
KL34-02	353.3	354.2	3.32	33200	2.18	5.8	730	86	39	52	2	68	3.1	15.0	110	0.01
KL34-02	354.2	356.3	2.08	20800	1.72	5.2	400	216	220	88	3	57	8.8	8.5	134	0.01
KL34-02	356.3	359.3	2.2	22000	2.06	4.5	700	289	290	34	2	64	9.8	10.2	175	0.01
KL34-02	359.3	362.3	1.75	17500	2.43	5	5050	1210	240	25	3	26	3.2	9.5	186	0.01
KL34-02	362.3	365.3	1.81	18100	2.3	2.8	770	304	200	51	3	23	11.9	10.7	139	0.01
KL34-02	365.3	368.3	3.14	31400	3.32	6	860	319	300	97	2	50	11.4	12.0	223	0.01
KL34-02	368.3	371.3	2.43	24300	2.91	4.3	1620	540	280	51	2	54	18	10.0	206	0.01
KL34-02	371.3	374.3	1.81	18100	2.71	3.1	780	328	260	48	0.01	25	14.1	8.0	211	0.01
KL34-02	374.3	377.3	2.04	20400	2.56	4.6	1770	330	360	16	0.01	26	14.5	8.0	163	0.44
KL34-02	377.3	380.3	2	20000	3.68	6.6	3450	620	530	57	4	82	19.6	12.0	207	0.8
KL34-02	380.3	383.3	1.86	18600	1.87	4.7	780	182	180	40	15	29	9.5	16.0	223	0.32
KL34-02	383.3	386.3	1.48	14800	1.66	3.8	700	1180	340	198	2	118	15.5	13.0	204	0.01
KL34-02	386.3	389.3	1.85	18500	1.56	3.1	560	294	480	700	0.01	51	15.3	5.5	126	0.01
KL34-02	389.3	392.3	1.58	15800	1.46	1.8	5700	203	320	257	1	71	20.5	9.0	18	0.01
KL34-02	392.3	394	1.99	19900	2	3.3	2050	299	390	105	2	193	14.8	7.5	140	0.01
KL34-02	394	396.1	3.22	32200	3.06	5	1110	920	360	1100	2	85	18.5	15.0	163	0.01
KL34-02	396.1	398.3	3.48	34800	3.82	13.5	2500	213	180	25	53	110	8.2	24.0	233	0.01
KL34-02	398.3	401.3	1.62	16200	2.36	11.3	276	79	150	64	12	37	3.9	19.0	245	0.1
KL34-02	401.3	404.3	3.02	30200	1.86	19.5	390	114	120	130	4	38	6.1	36.0	212	0.01
KL34-02	404.3	406.6	0.75	7500	0.73	15.2	1930	53	90	356	32	16	1.8	20.1	120	0.01
KL34-02	406.6	408.7	0.367	3670	0.37	5.7	246	72	150	197	18	13	1.8	9.3	142	0.01
KL34-02	408.7	410.3	0.42	4200	0.4	6.5	470	170	130	182	19	17	2.2	9.5	229	0.01
KL34-02	410.3	413.3	0.28	2800	0.14	1.8	420	116	120	264	3	12	3	6.8	254	0.01
KL34-02	413.3	416.3	0.25	2500	0.09	0.7	334	129	82	152	2	7	1.2	4.1	338	0.01
KL34-02	416.3	419.3	0.23	2300	0.11	1	346	73	90	265	2	9	1.1	4.0	232	0.1
KL34-02	419.3	422.3	0.21	2100	0.11	1.3	880	245	82	104	3	9	1.1	7.0	339	0.1
KL34-02	422.3	425.3	0.52	5200	0.23	2.1	620	127	130	41	11	16	1.7	11.8	265	0.15
KL34-02	425.3	428.3	0.85	8500	0.49	17.5	1610	295	130	161	66	16	1.8	15.7	227	0.1
KL34-02	428.3	431.4	0.55	5500	0.67	9.5	3800	480	140	62	21	13	2.5	7.8	396	0.38
KL34-02	431.4	434.5	0.89	8900	0.71	17.1	1750	265	70	100	29	17	2.5	8.5	445	0.18
KL34-02	434.5	437.5	1.39	13900	1.96	35.7	19900	910	89	96	23	19	1.6	15.5	318	0.18
KL34-02	437.5	440.3	1.7	17000	3.1	17.7	5600	3010	190	104	5	18	4.6	13.0	262	0.17
KL34-02	440.3	443.3	3.08	30800	2.88	8.8	1520	276	120	316	5	114	6.2	34.5	257	0.16
KL34-02	443.3	446.3	4.67	46700	3.02	10.5	1400	560	180	28	2	140	15.8	20.0	205	0.21
KL34-02	446.3	448.1	5.43	54300	3.92	10.8	2170	510	120	22	1	175	16.1	21.5	212	0.23
KL34-02	448.1	449.8	4.29	42900	3.5	11.3	2500	236	140	94	3	128	9	24.7	259	0.28
KL34-02	449.8	452.5	3.08	30800	2.42	11.1	2400	460	150	91	2	70	10.3	21.0	257	0.2
KL34-02	452.5	455.5	2.11	21100	1.48	6	1500	170	110	62	8	71	6.5	37.0	325	0.1
KL34-02	455.5	458.3	1.2	12000	1.39	4.5	920	83	44	58	6	81	2.4	66.0	301	0.01
KL34-02	458.3	460.9	1.38	13800	2.18	7.2	1910	167	70	32	8	56	1.4	73.0	331	0.01
KL34-02	460.9	463.9	2.27	22700	2.96	9.2	2600	178	54	27	38	19	1	60.0	313	0.26
KL34-02	463.9	467	1.69	16900	3.03	9.1	930	93	51	80	41	50	2.2	46.0	304	0.01
KL34-02	467	470	2.12	21200	3.21	12.3	2070	610	140	101	58	15	2.3	32.0	326	0.01
KL34-02	470	473	3.62	36200	2.82	10.9	700	73	170	142	5	26	3.6	36.0	290	0.36
KL34-02	473	476.1	3.12	31200	2.13	8.3	480	80	140	85	8	47	2	48.0	247	0.28
KL34-02	476.1	477.8	1.87	18700	1.36	8.7	7900	650	130	108	14	57	4.1	74.0	357	0.32
KL34-02	477.8	480.8	1.81	18100	3.16	7.7	1100	235	67	32	6	54	2.3	52.0	350	0.26
KL34-02	480.8	482.7	3.35	33500	3.34	12.6	930	129	140	97	8	50	2.8	35.0	304	0.01
KL34-02	482.7	485.8	2.37	23700	2.67	9.7	700	134	280	92	10	50	3	33.0	338	0.01
KL34-02	485.8	487	3.8	38000	3.19	16.2	2600	500	68	180	9	64	1.5	39.0	124	0.28
KL34-02	487	488.3	2.73	27300	1.9	11.2	2300	240	92	315	7	45	2.2	27.0	278	0.24
KL34-02	488.3	491.3	2.97	29700	1.53	10.9	1570	122	58	484	6	50	1.6	39.0	118	0.01
KL34-02	491.3	494.3	2.42	24200	1.76	9.6	1860	237	47	132	5	31	1.1	40.0	141	0.01
KL34-02	494.3	497.3	2.43	24300	1.42	8.5	2900	590	32	165	5	24	0.5	36.0	152	0.01
KL34-02	497.3	500.3	1.06	10600	0.98	5.8	327	358	7	15	5	15	0.5	11.7	35	0.01
KL34-02	500.3	503.3	2.05	20500	1.42	9.9	7500	1300	13	185	2	7	1.3	14.5	136	0.01
KL34-02	503.3	505.5	1.8	18000	1.19	9.8	7200	1160	19	247	3	12	1.6	12.0	126	0.01
KL34-02	505.5	508.6	3.35	33500	2.52	19.6	12900	3500	37	490	5	53	3.3	24.0	66	0.01
KL34-02	508.6	511.7	3.54	35400	2.56	34.2	29400	7100	44	1080	22	22	0.9	31.0	48	0.01
KL34-02	511.7	513.7	2.25	22500	1.68	28.2	34000	8800	73	56	48	26	2	25.0	50	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL34-02	513.7	515.3	2.27	22700	2.52	33.7	64500	8100	90	1060	29	16	1.1	52.5	48	0.01
KL34-02	515.3	518.3	1.67	16700	3.27	65	44700	38400	110	105	165	20	1.4	19.5	60	0.24
KL34-02	518.3	521.3	2.75	27500	3.23	46	66800	13900	210	128	73	25	2.6	26.0	76	0.2
KL34-02	521.3	524.3	2.41	24100	1.35	46	19000	40800	61	182	42	40	17.7	14.0	84	0.01
KL34-02	524.3	527.3	1.71	17100	1.77	27.9	26800	15100	64	45	56	53	5.8	31.0	75	0.01
KL34-02	527.3	529.5	2.32	23200	1.08	11.7	22300	2700	104	28	31	63	14.7	15.0	68	0.01
KL34-02	529.5	532.2	1.02	10200	1.21	9.4	33100	3300	190	24	13	15	3.4	17.9	57	0.01
KL34-02	532.2	535.6	1.98	19800	1.31	24.8	28900	4800	25	83	84	7	0.9	13.7	41	0.01
KL34-02	535.6	537.1	0.39	3900	1.43	10.7	82000	19600	52	6	27	8	1.3	27.0	34	0.01
KL34-02	537.1	539.3	0.78	7800	1.33	13.6	18100	2900	74	11	12	18	2.8	22.4	38	0.01
KL34-02	539.3	542.3	0.95	9500	1.33	25.6	6500	2900	92	12	82	28	1	22.7	29	0.01
KL34-02	542.3	545.3	0.74	7400	0.9	25.9	8400	4400	74	16	96	20	0.8	37.2	35	0.01
KL34-02	545.3	547.7	2.29	22900	1.75	24.5	5700	2600	180	13	43	53	1.8	10.0	30	0.01
KL34-02	547.7	549.9	2.31	23100	1.62	18.3	800	720	50	126	45	68	6.2	27.5	62	0.01
KL34-02	549.9	551.3	1.3	13000	1.36	12.9	401	188	55	19	36	37	1.9	19.9	49	0.01
KL34-02	551.3	554.3	3.25	32500	1.79	22.7	1100	153	35	32	22	31	1.3	34.0	42	0.01
KL34-02	554.3	557.3	1.78	17800	1.33	21	1710	103	59	170	49	20	0.9	28.2	54	0.01
KL34-02	557.3	560.3	1.68	16800	1	18.6	3200	387	54	1410	32	15	1	31.3	44	0.01
KL34-02	560.3	563.3	1.54	15400	1.27	24.7	6200	201	42	32	136	12	0.8	22.2	38	0.01
KL34-02	563.3	566.3	1.48	14800	1.32	21.7	3300	50	36	20	52	8	0.3	40.5	41	0.01
KL34-02	566.3	569.3	1.75	17500	1.53	21.8	11400	680	73	63	36	13	1.7	28.0	43	0.13
KL34-02	569.3	572.3	0.88	8800	0.99	7.1	17000	670	50	19	26	8	0.4	29.5	62	0.01
KL34-02	572.3	575.3	0.69	6900	0.66	3.8	14100	630	33	40	21	14	0.6	34.7	47	0.01
KL34-02	575.3	578.3	1.2	12000	0.95	4.4	8400	980	22	83	2	28	0.5	14.0	41	0.01
KL34-02	578.3	581.3	1	10000	0.83	3.4	19400	1470	58	54	14	19	0.3	13.3	34	0.01
KL34-02	581.3	584.3	0.85	8500	0.56	2.4	25200	1570	68	24	3	11	0.2	12.0	43	0.01
KL34-02	584.3	587.3	1.18	11800	0.81	3.3	21500	850	120	16	2	18	0.7	11.8	32	0.01
KL34-02	587.3	590.3	0.74	7400	0.58	2.6	13900	1570	42	30	2	15	0.6	14.5	33	0.01
KL34-02	590.3	593.3	0.83	8300	0.5	2.8	3700	321	23	89	7	22	0.2	24.4	63	0.01
KL34-02	593.3	596.3	0.61	6100	0.5	1.6	3900	230	13	28	0.01	17	0.01	9.5	52	0.01
KL34-02	596.3	598.8	1.01	10100	0.96	3	3800	180	22	12	2	28	0.2	16.3	54	0.01
KL34-02	598.8	600.6	0.57	5700	0.4	2.1	440	37	26	17	5	17	0.5	10.8	50	0.01
KL34-02	600.6	602.3	0.43	4300	0.37	1.3	408	62	9	6	1	15	0.01	10.0	46	0.01
KL34-02	602.3	605.3	0.82	8200	0.57	2	107	20	8	3	0.01	18	0.2	9.5	22	0.01
KL34-02	605.3	608.3	1.37	13700	1.29	3.3	104	30	20	22	2	20	0.4	17.3	30	0.01
KL34-02	608.3	611.3	0.92	9200	0.67	3.1	108	16	12	31	0.01	18	0.3	7.5	17	0.01
KL34-02	611.3	614.3	0.78	7800	0.75	4.2	1860	1100	59	70	3	16	2.6	34.2	44	0.25
KL34-02	614.3	617.3	0.73	7300	0.63	2.6	180	50	21	81	2	32	0.5	23.7	23	0.01
KL34-02	617.3	620.3	0.82	8200	0.48	3	720	101	11	184	1	13	0.2	11.4	26	0.01
KL34-02	620.3	623.3	0.6	6000	0.47	1.7	279	30	6	17	2	10	0.3	7.3	30	0.01
KL34-02	623.3	626.3	0.74	7400	0.35	2.4	105	15	3	141	0.01	13	0.2	9.8	24	0.01
KL34-02	626.3	629.3	1.41	14100	1.12	5.3	362	61	19	45	1	19	1.3	13.0	36	0.01
KL34-02	629.3	632.3	0.83	8300	0.91	3	286	20	9	72	3	11	6.2	11.5	29	0.01
KL34-02	632.3	635.3	2	20000	1.55	8.4	5000	1180	38	215	3	12	0.7	8.8	128	0.01
KL34-02	635.3	638.3	1.25	12500	1.51	4.7	202	32	5	4	3	15	0.2	4.8	51	0.01
KL34-02	638.3	639.1	0.37	3700	0.37	1.8	76	13	6	21	0.01	17	0.01	5.3	35	0.01
KL34-02	639.1	641.8	0.074	740	0.05	0.1	65	12	0.01	2	1	11	0.01	2.0	21	0.01
KL34-02	641.8	644	0.81	8100	0.38	3.1	240	22	6	53	3	25	0.01	8.8	44	0.01
KL34-02	644	646.6	0.62	6200	0.61	2.4	1410	30	32	15	16	14	0.6	34.5	43	0.01
KL34-02	646.6	649.6	0.27	2700	0.59	2.1	124	28	26	18	93	9	3.6	12.8	37	0.01
KL34-02	649.6	652.6	0.83	8300	1.07	4.6	102	13	21	17	9	18	0.5	12.0	94	0.01
KL34-02	652.6	655.3	0.84	8400	0.66	3.2	103	10	10	35	1	12	0.01	14.5	33	0.01
KL34-02	655.3	657.2	0.7	7000	0.42	2.6	79	33	7	52	1	16	0.01	32.5	100	0.01
KL34-02	657.2	659	0.5	5000	0.09	1.1	45	13	0.01	25	0.01	21	0.01	33.1	92	0.01
KL34-02	659	662	0.32	3200	0.07	1.3	53	12	2	114	1	21	0.2	24.8	110	0.01
KL34-02	662	665	0.23	2300	0.13	0.6	53	11	0.01	12	0.01	15	0.6	3.3	45	0.01
KL34-02	665	668	1.08	10800	0.57	3.3	104	15	0.01	39	0.01	28	0.01	9.0	53	0.01
KL34-02	668	671	0.186	1860	0.09	0.6	80	19	0.01	17	1	19	0.01	6.4	24	0.01
KL34-02	671	674	0.36	3600	0.2	1.2	184	116	3	19	0.01	20	0.01	5.0	25	0.01
KL34-02	674	676.5	0.35	3500	0.18	1.7	480	390	0.01	18	2	22	0.2	13.0	22	0.01
KL34-02	676.5	678.7	0.21	2100	0.23	0.7	67	13	4	26	0.01	32	0.01	7.5	52	0.01
KL34-02	678.7	681.7	0.46	4600	0.64	1.9	106	17	2	9	1	19	2.5	5.0	53	0.01
KL34-02	681.7	684.6	0.98	9800	0.89	3	105	18	6	10	1	20	0.01	10.0	61	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL34-02	684.6	687.6	0.8	8000	0.76	2.8	104	13	0.01	18	1	16	0.01	7.8	44	0.01
KL34-02	687.6	690.6	0.58	5800	0.87	2.7	95	12	0.01	7	1	13	0.01	5.5	70	0.01
KL34-02	690.6	693.6	0.29	2900	0.2	1	63	26	1	35	0.01	11	0.01	8.3	32	0.01
KL34-02	693.6	696.6	0.45	4500	0.27	1.8	67	20	3	232	1	11	0.01	6.0	44	0.01
KL34-02	696.6	699.7	0.38	3800	0.41	1.9	145	50	36	50	1	11	0.2	9.5	81	0.15
KL34-02	699.7	701	0.126	1260	0.15	0.7	156	60	23	375	1	9	0.01	8.8	74	0.16
KL34-02	701	704	0.22	2200	0.38	1.1	180	31	56	102	2	9	0.2	8.8	126	0.01
KL34-02	704	707	0.32	3200	0.44	2.2	136	67	57	42	2	14	0.8	13.8	86	0.01
KL34-02	707	710	0.38	3800	0.81	3	840	670	140	67	3	21	2.8	34.7	255	0.2
KL34-02	710	713	0.26	2600	0.4	2.2	1420	870	40	114	2	12	2	23.9	178	0.18
KL34-02	713	716	0.34	3400	0.28	1.8	68	16	12	39	0.01	8	0.01	4.3	85	0.01
KL34-02	716	719	0.73	7300	0.66	3.3	102	6	9	21	0.01	5	0.2	7.1	62	0.01
KL34-02	719	722	0.32	3200	0.29	2.6	318	170	42	13	1	6	1.3	5.8	55	0.01
KL34-02	722	725	0.4	4000	0.37	2.3	74	22	24	11	0.01	6	0.01	4.3	34	0.01
KL34-02	725	728	0.33	3300	0.37	2	180	18	13	79	2	7	0.01	6.3	32	0.01
KL34-02	728	731	0.201	2010	0.03	1.3	66	14	5	34	1	5	0.2	4.8	38	0.01
KL34-02	731	733.7	0.126	1260	0.1	1.2	136	50	32	30	0.01	5	0.4	3.8	33	0.01
KL34-03	0	4.2	0.009	90	0.04	0.9	1200	390	15	4	0.01	1	2.7	2.0	52	0.01
KL34-03	4.2	6	0.0024	24	0.03	0.7	391	189	7	2	0.01	1	1.7	0.5	29	0.01
KL34-03	6	9	0.0071	71	0.06	2.3	2400	374	13	3	0.01	1	2	0.5	26	0.28
KL34-03	9	12	0.0043	43	0.02	1.2	171	54	12	1	0.01	1	1.1	2.9	19	0.01
KL34-03	12	15	0.0307	307	0.03	1.2	680	150	15	1	0.01	1	1.3	3.5	28	0.01
KL34-03	15	18	0.0053	53	0.04	0.6	257	122	11	2	0.01	1	1	0.5	21	0.01
KL34-03	18	21	0.0018	18	0.03	0.9	171	120	19	1	0.01	1	1	1.0	20	0.01
KL34-03	21	23	0.0013	13	0.02	1.3	500	178	11	1	0.01	1	1.2	1.5	46	0.01
KL34-03	23	26.1	0.42	4200	0.2	15.3	7000	410	72	152	89	23	2	2.5	74	0.01
KL34-03	26.1	29.2	0.0031	31	0.01	1	800	490	15	1	1	2	1.8	0.8	23	0.01
KL34-03	29.2	32	0.016	160	0.13	3.7	1840	2390	35	3	1	1	6.7	3.9	21	0.12
KL34-03	32	34	0.0088	88	0.09	0.5	283	105	4	1	0.01	1	0.8	2.1	16	0.01
KL34-03	34	36	0.0053	53	0.06	0.5	328	181	12	1	0.01	1	1.9	0.5	19	0.01
KL34-03	36	39	0.0021	21	0.12	0.6	460	244	8	1	0.01	1	1.4	1.8	16	0.01
KL34-03	39	40.5	0.0056	56	0.08	1.1	790	950	13	1	0.01	1	1.9	4.4	17	0.01
KL34-03	40.5	42	0.493	4930	0.2	160	42600	180000	1550	16	116	4	103	123.0	47	1.15
KL34-03	42	45	0.0224	224	0.24	1.2	427	1120	15	2	0.01	1	2.8	3.3	18	0.01
KL34-03	45	48	0.0101	101	0.12	1.2	890	440	28	3	0.01	1	4.4	2.0	24	0.16
KL34-03	48	51	0.0027	27	0.06	0.1	180	54	20	1	0.01	1	0.8	1.5	25	0.01
KL34-03	51	54	0.0062	62	0.01	0.1	77	36	0.01	1	0.01	1	0.6	1.1	29	0.01
KL34-03	54	57	0.0074	74	0.01	0.1	53	32	7	1	0.01	1	0.5	1.3	42	0.01
KL34-03	57	60	0.006	60	0.01	0.1	54	31	4	2	0.01	1	0.2	2.0	35	0.01
KL34-03	60	63	0.0087	87	0.03	3.5	226	530	13	1	12	1	0.9	9.3	38	0.01
KL34-03	63	66	0.0073	73	0.03	4.5	730	540	59	3	21	3	1.5	18.0	125	0.01
KL34-03	66	69	0.0367	367	0.02	4.5	202	290	130	2	44	6	3.1	84.0	215	0.01
KL34-03	69	71.2	0.142	1420	0.04	12.9	2430	2180	490	6	39	5	17	49.5	237	0.14
KL34-03	71.2	74.3	0.0092	92	0.01	4.9	300	1380	19	5	15	1	3.2	32.5	33	0.01
KL34-03	74.3	77.4	0.011	110	0.01	14.7	430	1240	27	4	54	2	1.2	73.5	54	0.01
KL34-03	77.4	80.4	0.026	260	0.04	8.1	3050	2740	47	48	23	2	3.2	21.2	70	0.01
KL34-03	80.4	83.3	0.118	1180	0.08	2.5	500	386	32	21	18	1	1.8	3.5	37	0.01
KL34-03	83.3	85.5	1.27	12700	0.19	11.8	407	580	980	26	39	3	37	12.5	133	0.34
KL34-03	85.5	88.3	0.5	5000	0.16	7.6	410	217	510	30	7	4	363	5.8	128	0.3
KL34-03	88.3	90	2.88	28800	0.35	22.3	417	255	990	47	64	21	336	24.5	326	0.75
KL34-03	90	93	1.08	10800	0.11	8.9	560	430	190	36	8	5	369	10.8	138	0.27
KL34-03	93	96	1.06	10600	0.2	33	700	520	1000	45	24	12	285	27.0	143	0.43
KL34-03	96	99	0.326	3260	0.13	18	345	287	430	13	7	10	235	4.8	328	0.28
KL34-03	99	102	0.149	1490	0.08	4.7	139	249	150	10	6	7	58	6.9	353	0.01
KL34-03	102	105	0.61	6100	0.25	26.9	630	317	1160	11	51	2	264	5.8	305	0.38
KL34-03	105	108	0.82	8200	0.29	53	1930	4800	630	10	53	4	217	8.5	129	0.66
KL34-03	108	111	0.372	3720	0.25	11.5	174	253	1130	23	30	4	69	9.3	112	0.27
KL34-03	111	114	0.192	1920	0.77	19.4	1780	2690	670	59	39	3	42	11.0	95	0.2
KL34-03	114	117	0.364	3640	0.59	20.8	4600	4380	1280	197	52	3	91	11.5	105	0.54
KL34-03	117	120	0.39	3900	0.69	13.8	5600	2500	1020	758	45	4	88	6.4	72	0.58
KL34-03	120	122.4	1.04	10400	0.73	16.8	1670	1550	2050	450	63	17	125	24.0	105	0.74
KL34-03	122.4	123.8	0.0231	231	0.26	7.1	4940	2260	54	17	17	1	10.7	10.0	20	0.11
KL34-03	123.8	126	0.0064	64	0.09	2	600	263	20	14	7	1	2.9	5.7	16	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL34-03	126	128.2	0.0075		75	0.36	4.9	1720	630	55	52	20	3	3	8.7	19	0.01
KL34-03	128.2	129.4	0.0092		92	0.09	1	345	126	20	15	4	1	3.4	3.6	15	0.01
KL34-03	129.4	132	0.051		510	0.2	10.8	1200	1000	140	36	48	6	30	14.0	21	0.01
KL34-03	132	135	0.057		570	0.14	18.2	7700	1690	130	45	51	7	11.4	23.5	26	0.2
KL34-03	135	138	0.0201		201	0.19	18.1	1430	1760	83	20	42	1	6	17.8	30	0.01
KL34-03	138	141	0.074		740	1.34	33	9000	8500	190	85	62	3	80	41.0	41	1.08
KL34-03	141	142.7	0.0188		188	0.22	20.1	3230	4050	68	28	36	1	9.5	17.0	32	0.11
KL34-03	142.7	144.9	0.0332		332	0.49	16.2	7300	3100	64	70	34	1	10.3	17.5	36	0.21
KL34-03	144.9	147	0.0173		173	0.21	13.9	4740	3060	31	41	26	1	4.9	8.4	12	0.13
KL34-03	147	150	0.013		130	0.12	5.2	2430	2050	49	24	10	1	4.3	6.0	19	0.01
KL34-03	150	151.7	0.0078		78	0.06	2.3	1120	840	22	16	8	1	2.3	4.2	17	0.01
KL34-03	151.7	154.5	0.0063		63	0.03	1.6	410	910	11	20	4	1	1.5	2.5	11	0.01
KL34-03	154.5	157.4	0.13		1300	0.07	4.2	1100	1750	29	22	10	1	5.4	4.7	36	0.01
KL34-03	157.4	159.2	0.0157		157	0.08	4.1	1730	1550	30	13	6	1	3.7	5.2	12	0.01
KL34-03	159.2	162.1	0.0141		141	0.14	4.1	1450	1120	39	36	8	1	6	8.2	13	0.01
KL34-03	162.1	165	0.105		1050	0.72	64	36400	25100	250	763	181	4	45	93.0	29	0.35
KL34-03	165	167.6	0.0138		138	0.15	5.8	1920	2320	65	18	3	1	7	5.2	11	0.12
KL34-03	167.6	170.7	0.0241		241	0.13	5.9	2000	3590	36	17	7	1	5.6	7.5	9	0.1
KL34-03	170.7	172.5	0.0374		374	0.35	35	14000	10800	42	55	65	1	10	33.0	20	0.27
KL34-03	172.5	175.1	0.0139		139	0.07	3.7	3600	3660	19	6	3	1	4	5.8	9	0.01
KL34-03	175.1	177	0.0063		63	0.09	6.9	11300	10000	16	6	2	1	5.7	6.7	12	0.01
KL34-03	177	180	0.0062		62	0.08	1.8	1780	1070	21	14	2	1	2.2	3.1	10	0.01
KL34-03	180	182.3	0.0165		165	0.05	1.8	1220	790	22	12	3	1	0.9	2.9	14	0.01
KL34-03	182.3	185.8	0.0189		189	0.06	6.7	2670	2330	45	36	22	1	3	16.0	50	0.01
KL34-03	185.8	188.3	0.0057		57	0.07	1.6	3340	1780	24	7	1	1	1.8	2.6	10	0.01
KL34-03	188.3	191.3	0.0115		115	0.05	1.7	397	610	13	9	2	1	1.7	2.4	13	0.01
KL34-03	191.3	194.4	0.007		70	0.06	5.7	630	640	28	5	9	5	1.6	6.9	14	0.01
KL34-03	194.4	196.3	0.0079		79	0.03	1.8	660	560	19	5	2	1	1.9	4.6	11	0.01
KL34-03	196.3	198	0.0091		91	0.08	5.4	1600	4260	22	13	3	1	5.6	4.0	9	0.13
KL34-03	198	200.8	0.0067		67	0.03	0.9	250	355	8	8	1	1	1.4	2.2	14	0.01
KL34-03	200.8	203.5	0.0051		51	0.01	0.7	600	331	12	7	1	1	2.7	2.5	11	0.01
KL34-03	203.5	206.6	0.0064		64	0.02	1.2	440	570	13	10	1	1	3	2.3	16	0.01
KL34-03	206.6	209.5	0.0054		54	0.03	1.4	850	570	19	11	2	1	4.8	2.8	14	0.01
KL34-03	209.5	212.6	0.0037		37	0.05	1.5	800	610	14	22	3	1	3.3	5.5	13	0.01
KL34-03	212.6	215.6	0.0079		79	0.23	1.7	1960	440	41	12	4	1	4.1	4.1	15	0.01
KL34-03	215.6	218.3	0.0076		76	0.34	4.6	4700	2380	48	15	4	1	7.7	3.9	16	0.28
KL34-03	218.3	220.4	0.0087		87	0.37	8.4	8100	4500	37	12	4	1	13.8	5.0	14	0.23
KL34-03	220.4	222	0.0083		83	0.09	3.1	1770	1050	27	4	1	1	5.1	6.5	15	0.01
KL34-03	222	225	0.0064		64	0.04	1	670	490	36	26	2	1	2.8	1.8	25	0.01
KL34-03	225	228	0.046		460	0.77	7.6	28100	3600	140	34	4	1	28	13.3	18	4.07
KL34-03	228	231	0.83		8300	0.37	20.1	7300	4300	780	19	36	1	42	3.9	17	0.41
KL34-03	231	234	0.152		1520	0.26	13	7200	5300	180	20	22	2	15	4.5	22	0.33
KL34-03	234	237	0.205		2050	0.34	8.5	1680	1110	81	28	7	4	3.4	22.0	40	0.01
KL34-03	237	239.1	0.0072		72	0.05	2.3	800	620	21	13	5	1	0.8	4.0	17	0.01
KL34-03	239.1	241.5	0.0107		107	0.09	5.6	2980	2240	33	29	10	1	4.5	3.5	13	0.01
KL34-03	241.5	244.4	0.072		720	0.11	4.1	2130	1000	38	26	17	2	2.6	4.8	15	0.01
KL34-03	244.4	246.1	0.0297		297	0.06	3.4	860	520	38	74	18	1	1.4	4.8	14	0.01
KL34-03	246.1	248.6	0.141		1410	0.33	18.6	1960	910	60	27	147	3	0.8	33.1	19	0.01
KL34-03	248.6	251.4	0.33		3300	0.61	11	1220	314	28	10	33	18	2.3	25.0	20	0.01
KL34-03	251.4	254.4	0.201		2010	0.3	6.2	750	317	74	150	32	11	3.7	11.0	37	0.01
KL34-03	254.4	257.5	0.0303		303	0.05	1	134	61	10	710	30	3	0.8	2.5	72	0.01
KL34-03	257.5	259.3	0.126		1260	0.16	2.2	297	210	58	1020	26	6	3.3	8.0	44	0.01
KL34-03	259.3	261	0.085		850	0.06	1	145	80	13	450	3	5	2.6	3.0	22	0.01
KL34-03	261	264	0.21		2100	0.07	2.3	230	172	24	170	29	8	1.9	8.3	40	0.01
KL34-03	264	267	0.071		710	0.08	1.7	186	67	21	480	10	7	1.4	4.3	71	0.01
KL34-03	267	270	0.94		9400	0.45	12.3	4200	177	120	240	22	87	3.7	10.3	17	0.01
KL34-03	270	272.3	0.61		6100	0.18	15.8	3600	145	38	18	20	36	2.1	9.0	28	0.01
KL34-03	272.3	275.2	0.0117		117	0.05	2.5	1100	364	46	5	2	2	4.6	1.5	19	0.01
KL34-03	275.2	278.3	0.21		2100	0.13	10.2	4100	355	21	46	121	7	1.8	7.5	19	0.01
KL34-03	278.3	280.4	0.21		2100	0.09	9.1	2300	264	25	42	120	7	1.3	5.0	18	0.01
KL34-03	280.4	281.9	0.395		3950	0.47	11.2	4700	610	280	250	83	15	5	8.0	20	1.34
KL34-03	281.9	284.9	0.74		7400	0.75	23.6	15300	1770	360	10	202	22	9	9.3	40	0.39
KL34-03	284.9	287.9	0.61		6100	0.66	19.4	2700	361	58	200	66	20	1.3	9.0	13	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL34-03	287.9	291	1.03	10300	1.8	16.3	7600	1410	290	13	75	19	6.9	25.5	20	0.36
KL34-03	291	294	0.78	7800	0.52	6.6	4200	1940	78	200	10	13	5.6	19.5	69	0.1
KL34-03	294	297	0.42	4200	0.38	22.5	1600	2700	100	79	48	5	15.5	13.8	56	0.15
KL34-03	297	300	2.53	25300	2.04	6.9	690	275	100	10	3	84	4.3	31.0	105	1.05
KL34-03	300	303	1.27	12700	2.8	253	3700	10500	610	3	152	21	14	23.0	108	1.43
KL34-03	303	306	2.94	29400	1.46	15.6	750	2900	70	19	7	108	2.4	55.0	36	0.2
KL34-03	306	309	4.18	41800	1.72	12.7	160	1080	100	4	3	78	3.6	41.0	133	0.4
KL34-03	309	312	3.05	30500	2.16	6.6	77	186	6	3	2	62	0.6	27.0	60	0.01
KL34-03	312	315	0.58	5800	2.18	68	20500	20900	94	30	218	15	17	33.0	208	1.37
KL34-03	315	316.8	3.3	33000	0.98	9.8	860	500	2000	26	3	95	250	38.5	179	5.63
KL34-03	316.8	318	0.47	4700	0.15	1.4	540	134	390	272	1	23	26	23.8	116	0.82
KL34-03	318	321	0.99	9900	0.31	6.8	3300	700	1890	32	3	20	720	20.8	142	0.01
KL34-03	321	324	1.03	10300	0.4	14.4	8700	4200	2000	139	4	26	1340	26.5	169	13.4
KL34-03	324	327	1.15	11500	0.2	2.4	407	310	360	57	0.01	24	90	13.3	140	0.65
KL34-03	327	330	0.45	4500	0.11	0.9	370	132	180	46	1	23	2.5	28.3	117	0.24
KL34-03	330	333	0.37	3700	0.08	0.9	134	83	100	140	0.01	22	1.8	18.3	103	0.1
KL34-03	333	336	0.48	4800	0.11	1	107	76	250	77	1	33	2.4	15.6	75	0.12
KL34-03	336	339	0.38	3800	0.1	2	224	195	140	62	0.01	35	18.5	19.0	111	0.17
KL34-03	339	342.1	0.62	6200	0.25	1.7	82	76	50	33	2	22	1.5	12.8	80	0.01
KL34-03	342.1	345	0.81	8100	0.11	2.1	39	23	15	46	0.01	25	1	15.5	132	0.01
KL34-03	345	348	1.25	12500	0.37	3	42	28	46	47	0.01	46	2	20.5	113	0.01
KL34-03	348	351	0.96	9600	0.26	2.7	1350	278	430	71	4	46	5.2	15.8	94	0.35
KL34-03	351	354	0.67	6700	0.23	1.7	95	40	37	131	0.01	23	0.8	10.3	111	0.01
KL34-03	354	357	0.71	7100	0.14	3.5	2200	930	160	910	0.01	5	6.6	6.8	187	0.43
KL34-03	357	360	1.28	12800	0.15	3.3	560	326	91	130	0.01	18	3	10.5	93	0.12
KL34-03	360	363	0.87	8700	0.1	1.9	297	58	11	180	3	16	1	6.3	87	0.01
KL34-03	363	366	0.7	7000	0.06	1.4	45	21	6	190	0.01	10	1	8.2	86	0.01
KL34-03	366	368.6	1	10000	0.1	1.6	67	45	9	290	0.01	13	1	11.3	74	0.01
KL34-03	368.6	371.6	0.72	7200	0.31	1.8	47	12	5	160	1	10	1.2	6.8	80	0.01
KL34-03	371.6	374.6	0.71	7100	0.22	1.5	72	23	7	85	1	10	1.5	7.3	82	0.01
KL34-03	374.6	376	1.02	10200	0.15	1.9	81	26	12	320	0.01	14	6.7	7.0	104	0.01
KL34-03	376	378	1.05	10500	0.38	2.7	383	83	22	151	2	13	1.7	7.8	76	0.01
KL34-03	378	381	0.9	9000	0.27	1.6	68	23	25	340	0.01	11	0.6	11.8	68	0.01
KL34-03	381	384	0.9	9000	0.43	2.2	165	95	62	530	0.01	21	2.1	12.0	40	0.01
KL34-03	384	386	1.21	12100	0.24	3.5	710	590	290	294	1	27	52	11.0	21	0.61
KL34-03	386	388.9	2.91	29100	1.11	5	312	164	120	210	0.01	27	28	21.0	152	0.25
KL34-03	388.9	391.3	2.25	22500	0.91	2.5	169	47	11	310	0.01	30	2	16.5	128	0.14
KL34-03	391.3	393	0.89	8900	0.24	1.5	361	160	10	150	0.01	11	1.3	8.8	178	0.01
KL34-03	393	396	0.93	9300	0.19	4.9	249	127	480	650	3	7	135	8.0	87	0.39
KL34-03	396	399	0.71	7100	0.21	5.1	520	3200	1100	1490	3	5	125	5.8	118	0.63
KL34-03	399	401.2	0.4	4000	0.1	0.8	183	267	210	230	0.01	4	10.3	4.5	119	0.18
KL34-03	401.2	403.7	0.42	4200	0.1	1	350	181	54	900	0.01	6	1.6	5.8	184	0.11
KL34-03	403.7	406.3	0.48	4800	0.14	1.2	307	151	39	190	0.01	16	1.5	10.7	114	0.01
KL34-03	406.3	408.2	0.52	5200	0.09	1	299	185	32	390	0.01	5	1.7	5.5	258	0.01
KL34-03	408.2	411.2	0.88	8800	0.31	1.1	120	31	7	280	1	6	1	6.5	269	0.01
KL34-03	411.2	414	0.78	7800	0.21	0.9	84	31	5	230	0.01	8	0.5	7.5	206	0.01
KL34-03	414	417	2.91	29100	1.45	2.3	62	8	4	72	0.01	20	0.5	17.5	129	0.01
KL34-03	417	420	0.79	7900	0.18	1.6	330	137	14	150	0.01	11	0.7	10.0	296	0.01
KL34-03	420	422.9	0.29	2900	0.07	1.5	254	121	15	110	0.01	6	1.5	4.0	274	0.01
KL34-03	422.9	426	0.47	4700	0.07	1.4	196	92	6	172	0.01	6	0.5	5.3	122	0.01
KL34-03	426	428.3	0.52	5200	0.09	1.2	67	30	5	370	0.01	8	0.3	5.5	128	0.01
KL34-03	428.3	431.1	0.47	4700	0.12	0.9	405	247	120	180	0.01	8	1.9	5.3	120	0.14
KL34-03	431.1	434.1	0.58	5800	0.12	1.2	164	60	18	130	0.01	13	0.7	7.5	98	0.01
KL34-03	434.1	436	0.49	4900	0.05	1	81	20	8	78	0.01	9	0.4	6.3	102	0.01
KL34-03	436	438	0.57	5700	0.08	1	194	78	15	160	0.01	4	1.9	4.7	94	0.01
KL34-03	438	441	0.84	8400	0.18	1.5	87	75	12	920	0.01	7	0.3	8.3	135	0.01
KL34-03	441	444	0.52	5200	0.14	1	77	61	3	210	0.01	6	0.3	7.0	155	0.01
KL34-03	444	447	0.45	4500	0.13	0.7	47	20	3	47	0.01	7	0.6	7.5	328	0.01
KL34-03	447	450	0.79	7900	0.26	1.3	26	15	76	53	0.01	11	0.6	9.4	350	0.01
KL34-03	450	453	0.51	5100	0.09	0.8	23	18	43	250	0.01	7	0.3	6.8	170	0.01
KL34-03	453	456	0.77	7700	0.12	1.3	39	35	170	47	0.01	10	0.8	7.8	154	0.01
KL34-03	456	458.1	1.04	10400	0.21	2.1	78	67	290	52	0.01	12	1.4	7.3	251	0.01
KL34-03	458.1	461.1	0.53	5300	0.13	1.3	40	41	130	35	1	7	1.9	5.7	379	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL34-03	461.1	464.2	1.24	12400	0.16	2.4	149	385	1000	95	0.01	10	4.6	8.5	186	0.01
KL34-03	464.2	467	1.2	12000	0.15	2.2	60	37	24	53	0.01	10	0.6	8.9	180	0.01
KL34-03	467	470	0.89	8900	0.2	1.4	23	45	11	35	0.01	9	0.2	5.0	198	0.01
KL34-03	470	472.1	0.95	9500	0.09	1.7	279	580	1260	44	0.01	7	5.4	8.5	154	0.01
KL34-03	472.1	474	0.785	7850	0.1	1.5	25	30	670	61	0.01	9	0.7	7.8	145	0.01
KL34-03	474	477	0.84	8400	0.11	1.4	18	15	220	236	0.01	7	0.5	8.5	324	0.01
KL34-03	477	479	0.84	8400	0.09	1.5	19	15	39	90	0.01	10	0.4	9.6	319	0.01
KL34-03	479	481.2	1.17	11700	0.1	3.7	1760	980	490	56	2	7	15.5	11.8	146	0.79
KL34-03	481.2	483	0.96	9600	0.12	1.8	940	307	33	47	0.01	7	1.2	8.5	125	0.14
KL34-03	483	486	0.73	7300	0.12	1.2	47	23	6	49	0.01	8	0.5	6.8	112	0.01
KL34-03	486	489	0.75	7500	0.17	2.1	740	325	28	130	0.01	8	0.7	7.8	113	0.01
KL34-03	489	492	1.13	11300	0.18	14.3	2600	1490	150	90	11	7	8.9	10.9	129	0.34
KL34-03	492	495	1.24	12400	0.12	2.1	108	47	59	74	0.01	9	0.01	8.4	133	0.01
KL34-03	495	498	1.04	10400	0.08	1.5	55	26	36	33	0.01	10	0.01	10.4	121	0.01
KL34-03	498	501	0.71	7100	0.04	0.9	480	423	27	50	0.01	7	2	3.8	142	0.01
KL34-03	501	504	0.86	8600	0.05	0.6	73	38	38	195	0.01	15	0.5	4.3	118	0.01
KL34-03	504	507	0.795	7950	0.07	1.6	232	151	290	188	1	10	17.2	4.5	153	0.16
KL34-03	507	510	0.65	6500	0.1	1.5	82	100	210	160	1	8	2	4.3	150	0.14
KL34-03	510	513	0.73	7300	0.12	4.7	321	118	1790	530	0.01	8	10	4.5	148	0.24
KL34-03	513	516	0.67	6700	0.25	2	99	73	420	110	0.01	12	2.6	6.1	152	0.1
KL34-03	516	519	0.9	9000	0.18	1.5	118	91	1180	165	0.01	10	3.1	3.5	169	0.01
KL34-03	519	522	0.86	8600	0.13	1.6	103	17	400	121	0.01	13	1.1	5.0	143	0.01
KL34-03	522	525	0.7	7000	0.14	1.3	33	10	7	107	0.01	11	0.3	7.3	137	0.01
KL34-03	525	528	0.86	8600	0.17	1.9	56	16	9	185	0.01	12	0.01	4.9	123	0.01
KL34-03	528	531	0.825	8250	0.06	2.1	840	510	380	133	0.01	11	9.7	4.8	123	0.34
KL34-03	531	534	0.605	6050	0.08	1.3	49	32	270	244	0.01	11	1.1	6.2	121	0.01
KL34-03	534	537	0.635	6350	0.09	3.6	382	56	1875	167	2	12	24	5.0	130	0.6
KL34-03	537	540	0.535	5350	0.06	8.5	76	47	110	165	1	8	5	4.0	151	0.18
KL34-03	540	543	0.44	4400	0.04	1	122	50	40	53	0.01	9	3.4	3.8	142	0.01
KL34-03	543	546	0.79	7900	0.09	1.9	430	101	64	233	0.01	9	18.5	5.0	152	0.21
KL34-03	546	549	0.79	7900	0.08	3.3	830	387	220	267	1	8	34	6.0	123	0.29
KL34-03	549	552	2.16	21600	0.24	4.1	434	109	60	163	0.01	25	0.01	15.5	104	0.1
KL34-03	552	555	3.01	30100	1.09	3.9	161	14	5	155	0.01	57	5.1	40.0	39	0.12
KL34-03	555	558	1.25	12500	0.67	2	252	10	7	9	0.01	36	0.01	6.8	24	0.01
KL34-03	558	561	1.28	12800	0.4	1.9	113	11	4	14	0.01	34	0.01	8.2	24	0.01
KL34-03	561	564	1.42	14200	0.34	3.6	101	11	2	33	0.01	33	0.01	7.0	56	0.01
KL34-03	564	566.8	0.65	6500	0.25	1.4	97	11	3	4	0.01	37	1	6.3	40	0.01
KL34-03	566.8	569	0.149	1490	0.07	0.1	81	14	0.01	11	0.01	17	0.9	2.5	53	0.01
KL34-03	569	572.1	0.64	6400	0.22	1.7	76	11	1	24	0.01	29	0.01	6.3	26	0.01
KL34-03	572.1	575.2	0.185	1850	0.08	0.7	56	8	2	9	0.01	30	0.5	3.2	29	0.01
KL34-03	575.2	578.3	0.274	2740	0.1	0.8	84	10	2	34	0.01	18	0.4	4.3	19	0.01
KL34-03	578.3	581.4	0.332	3320	0.14	1	97	12	1	24	0.01	31	1.2	5.3	49	0.01
KL34-03	581.4	583.9	1.21	12100	0.26	3.2	165	10	1	66	0.01	47	0.01	32.0	24	0.01
KL34-03	583.9	585.7	0.342	3420	0.08	1	92	9	0.01	17	0.01	32	0.01	7.8	22	0.01
KL34-03	585.7	588	0.393	3930	0.17	1.4	101	9	1	6	0.01	34	0.01	8.3	47	0.01
KL34-03	588	591	0.89	8900	0.32	2.3	129	13	3	87	0.01	41	0.01	15.6	39	0.01
KL34-03	591	594	0.59	5900	0.27	1.8	125	7	0.01	6	0.01	33	0.01	6.5	59	0.01
KL34-03	594	597	0.8	8000	0.23	2.1	81	135	1	52	0.01	16	0.01	8.1	103	0.01
KL34-03	597	600	1.02	10200	0.32	2.8	70	6	1	23	0.01	19	0.01	9.3	126	0.01
KL34-03	600	603	0.437	4370	0.16	1.3	56	5	0.01	36	0.01	15	0.01	7.0	143	0.01
KL34-03	603	606	0.194	1940	0.08	0.1	65	6	1	7	0.01	28	0.01	4.0	44	0.01
KL34-03	606	609	0.255	2550	0.08	1	69	8	2	21	0.01	48	0.01	18.9	60	0.01
KL34-03	609	612	0.464	4640	0.15	1.3	84	6	5	20	0.01	36	1	8.7	31	0.01
KL34-03	612	615	0.5	5000	0.17	1.6	70	8	1	43	1	24	0.01	8.8	40	0.01
KL34-03	615	618	0.249	2490	0.06	0.8	57	8	8	24	0.01	27	0.01	5.9	32	0.01
KL34-03	618	621	0.178	1780	0.03	0.5	27	8	1	9	0.01	9	0.01	3.6	19	0.01
KL34-03	621	623.4	0.53	5300	0.26	2.3	143	14	1	45	0.01	29	0.01	13.1	46	0.01
KL34-03	623.4	626	0.35	3500	0.15	1.2	99	10	0.01	57	0.01	32	0.3	21.0	53	0.01
KL34-03	626	628.5	0.348	3480	0.13	0.9	119	8	2	27	0.01	21	0.01	11.7	47	0.01
KL34-03	628.5	631.6	0.138	1380	0.06	0.1	60	8	4	16	0.01	15	0.01	7.0	44	0.01
KL34-03	631.6	634.6	0.63	6300	0.17	1.4	40	10	5	30	0.01	14	0.01	13.3	67	0.01
KL34-03	634.6	637.1	0.78	7800	0.15	2.1	78	247	46	108	1	13	11.3	6.7	317	0.1
KL34-03	637.1	639	0.038	380	0.02	0.1	49	121	19	139	0.01	5	0.8	3.3	155	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL34-03	639	642	0.059		590	0.01	0.1	91	50	12	290	0.01	14	0.01	8.4	331	0.01
KL34-03	642	645	0.152		1520	0.01	0.1	145	87	28	400	0.01	8	0.01	5.3	114	0.01
KL34-03	645	648	0.183		1830	0.01	0.1	114	50	23	156	0.01	5	1	8.8	102	0.01
KL34-03	648	651	0.175		1750	0.01	0.1	39	48	19	168	0.01	9	1	6.5	230	0.01
KL34-03	651	654	0.258		2580	0.01	0.1	37	25	4	95	0.01	6	0.01	3.7	206	0.01
KL34-03	654	657	0.212		2120	0.01	0.1	37	35	6	64	0.01	6	0.6	3.3	207	0.01
KL34-03	657	660	0.28		2800	0.02	0.1	38	28	0.01	107	0.01	7	0.01	3.5	71	0.01
KL34-03	660	663	0.209		2090	0.01	0.1	84	64	1	41	0.01	7	0.01	3.9	203	0.01
KL34-03	663	666	0.259		2590	0.02	0.6	70	47	78	125	0.01	7	0.01	3.8	95	0.01
KL34-03	666	669	0.219		2190	0.01	0.1	36	48	5	82	0.01	4	0.01	3.5	56	0.01
KL34-03	669	672	0.245		2450	0.01	0.1	35	22	1	70	0.01	4	0.01	3.0	65	0.01
KL34-03	672	675	0.189		1890	0.01	0.1	47	21	1	104	0.01	7	0.01	3.8	182	0.01
KL34-03	675	678	0.227		2270	0.06	2.2	72	35	100	209	0.01	6	0.01	4.0	45	0.15
KL34-03	678	681	0.164		1640	0.05	2.6	48	100	92	71	0.01	13	0.01	5.5	93	0.27
KL34-03	681	684	0.213		2130	0.03	0.7	33	23	2	56	0.01	7	0.01	3.6	107	0.01
KL34-03	684	687	0.181		1810	0.02	0.8	33	25	15	200	0.01	6	1	3.2	102	0.01
KL34-03	687	690	0.241		2410	0.05	1.2	100	210	65	169	1	16	9.9	6.8	91	0.1
KL34-03	690	693	0.197		1970	0.03	0.1	39	33	8	135	0.01	8	0.8	2.9	247	0.01
KL34-03	693	696	0.305		3050	0.1	1.3	45	30	3	170	1	7	0.3	4.3	84	0.01
KL34-03	696	699	0.186		1860	0.03	0.7	43	24	4	67	0.01	8	0.4	5.3	105	0.01
KL34-03	699	702	0.189		1890	0.01	1.4	90	63	60	112	1	6	1.6	3.3	93	0.13
KL34-03	702	705	0.193		1930	0.01	0.8	74	47	18	54	1	6	0.5	5.0	124	0.01
KL34-03	705	708	0.223		2230	0.02	0.9	65	42	9	51	0.01	6	0.8	3.7	231	0.01
KL34-03	708	711	0.167		1670	0.02	1.3	93	44	190	61	0.01	5	1.4	7.2	113	0.01
KL34-03	711	714	0.387		3870	0.03	6.3	306	76	790	121	22	6	11.3	4.4	100	0.12
KL34-03	714	717	0.183		1830	0.01	0.1	68	39	16	88	0.01	4	0.5	2.4	96	0.01
KL34-03	717	720	0.2		2000	0.02	1.2	62	35	140	140	6	20	2.5	10.3	100	0.01
KL34-03	720	723	0.168		1680	0.02	0.8	80	55	2	49	0.01	6	0.9	2.5	242	0.01
KL34-03	723	726	0.136		1360	0.01	1	70	64	6	90	0.01	7	0.7	2.9	240	0.01
KL34-03	726	729	0.207		2070	0.01	4.3	65	44	110	37	2	6	1.5	3.8	224	0.01
KL34-03	729	732	0.266		2660	0.04	4.7	201	65	600	99	3	7	33	3.6	247	0.01
KL34-03	732	734.7	0.223		2230	0.03	9.9	144	197	250	46	1	9	1.3	7.6	231	0.17
KL34-04	0	3.6	0.0157		157	0.05	0.5	410	170	7	14	0.01	1	0.8	1.2	24	0.01
KL34-04	3.6	6.3	0.003		30	0.02	0.7	460	139	7	5	0.01	1	1	1.3	23	0.01
KL34-04	6.3	10.2	0.0041		41	0.01	1.2	740	225	17	4	0.01	1	1.8	2.1	22	0.01
KL34-04	10.2	14.6	0.0031		31	0.01	1.3	430	204	16	4	0.01	1	1.9	2.5	16	0.01
KL34-04	14.6	17.7	0.0122		122	0.01	0.9	331	145	11	8	0.01	1	0.8	1.9	14	0.01
KL34-04	17.7	20.8	0.0012		12	0.01	0.1	114	69	17	3	0.01	3	0.4	1.1	21	0.01
KL34-04	20.8	23.6	0.0046		46	0.07	1.1	590	240	14	6	0.01	2	1.8	1.8	18	0.01
KL34-04	23.6	26.7	0.0045		45	0.05	1.7	1190	550	21	4	0.01	1	1.4	4.6	25	0.01
KL34-04	26.7	29.8	0.0085		85	0.01	0.1	100	60	9	3	0.01	1	0.01	1.9	24	0.01
KL34-04	29.8	32.8	0.004		40	0.08	0.1	266	100	11	3	0.01	1	0.6	1.5	21	0.01
KL34-04	32.8	35.8	0.0189		189	0.04	1.1	600	255	22	2	1	1	1.3	1.6	24	0.01
KL34-04	35.8	38.8	0.0071		71	0.03	0.1	303	130	7	3	0.01	1	0.4	1.3	16	0.01
KL34-04	38.8	41.6	0.0053		53	0.23	0.1	335	124	9	5	0.01	1	1.1	1.9	20	0.01
KL34-04	41.6	44.8	0.0023		23	0.02	1.2	96	174	7	4	2	1	0.3	3.4	21	0.01
KL34-04	44.8	47	0.0371		371	0.03	25	14100	15900	77	5	35	2	6.2	13.6	20	0.18
KL34-04	47	50.8	0.177		1770	0.14	48	2500	31400	590	10	19	2	13.3	25.9	19	0.17
KL34-04	50.8	53.5	0.0045		45	0.03	1.2	510	910	19	6	0.01	1	1.6	3.1	20	0.01
KL34-04	53.5	56.6	0.0041		41	0.03	1.1	385	920	38	4	0.01	1	1.4	1.5	30	0.01
KL34-04	56.6	59.7	0.0185		185	0.01	1	248	580	24	2	0.01	1	1.8	1.4	20	0.01
KL34-04	59.7	62.8	0.003		30	0.01	0.7	560	550	13	4	0.01	2	0.6	2.0	33	0.01
KL34-04	62.8	65.2	0.0066		66	0.02	2.6	450	1110	35	5	4	1	2.8	9.4	40	0.01
KL34-04	65.2	68.8	0.0114		114	0.01	3.5	560	255	35	10	16	1	1.2	10.0	45	0.01
KL34-04	68.8	71.8	0.0153		153	0.01	11.8	1740	1710	39	7	32	1	2.8	14.8	29	0.01
KL34-04	71.8	74.8	0.0053		53	0.01	22.2	262	1930	29	5	55	1	1.1	21.2	34	0.01
KL34-04	74.8	77.8	0.0046		46	0.01	36.8	500	4850	25	33	86	1	1	58.0	28	0.01
KL34-04	77.8	80.8	0.0156		156	0.14	29	1570	3410	140	42	159	1	4.2	53.5	39	0.2
KL34-04	80.8	83.8	0.0042		42	0.06	1.5	650	600	100	39	3	1	2.3	12.9	25	0.1
KL34-04	83.8	86.8	0.0121		121	0.01	5.9	590	1470	78	77	26	2	1.6	22.0	42	0.01
KL34-04	86.8	89.8	0.0207		207	0.01	0.9	98	135	46	30	3	1	0.8	5.5	25	0.01
KL34-04	89.8	92.8	0.0113		113	0.01	4.1	405	378	39	19	26	1	1.1	15.5	54	0.01
KL34-04	92.8	95.8	0.171		1710	0.01	5.8	1640	740	150	920	50	8	3.5	12.4	68	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL34-04	95.8	98.8	0.055		550	0.02	1.2	139	90	120	35	6	4	4.3	4.4	75	0.01
KL34-04	98.8	101.8	0.0389		389	0.02	0.1	168	105	61	32	1	4	1.8	1.8	120	0.01
KL34-04	101.8	104.8	0.0131		131	0.01	0.7	288	221	30	39	2	3	1	1.4	145	0.01
KL34-04	104.8	106.4	0.0327		327	0.01	0.6	227	108	25	17	2	2	1.6	1.0	87	0.01
KL34-04	106.4	109.7	0.63		6300	0.16	21.8	3530	1780	750	28	122	23	49	2.8	65	0.34
KL34-04	109.7	112.1	9.82		98200	0.66	102	20000	12600	2600	90	244	4	570	15.0	80	1.39
KL34-04	112.1	115.5	0.144		1440	0.14	7.1	3230	1800	390	29	18	6	30	7.8	66	0.15
KL34-04	115.5	118.8	0.184		1840	0.06	13.2	4500	8000	470	30	17	2	33	6.0	84	0.43
KL34-04	118.8	122	0.098		980	0.05	4.7	860	900	180	17	7	1	16.9	4.9	92	0.1
KL34-04	122	125.8	0.048		480	0.08	3.3	365	209	140	18	20	4	5	5.4	155	0.01
KL34-04	125.8	128	0.0112		112	0.06	1.4	210	117	37	26	4	1	1.7	2.0	102	0.01
KL34-04	128	131	0.0117		117	0.11	2.3	389	540	61	39	6	3	4.7	3.9	67	0.01
KL34-04	131	134.8	0.172		1720	0.13	5.2	740	480	660	51	12	3	19	3.8	91	0.11
KL34-04	134.8	137.7	0.168		1680	0.27	8	620	560	610	530	21	6	30	6.0	58	0.14
KL34-04	137.7	140.8	0.055		550	0.59	5.3	620	730	260	1320	18	7	41	5.5	65	0.13
KL34-04	140.8	143.8	0.3		3000	1.22	14.6	6600	1110	840	3625	84	21	24	0.9	75	0.22
KL34-04	143.8	145.1	0.025		250	0.05	2.9	850	372	20	115	11	4	1.6	6.1	14	0.01
KL34-04	145.1	148.1	0.024		240	0.16	6.5	293	420	96	380	32	3	4.7	15.7	42	0.01
KL34-04	148.1	151	0.0086		86	0.07	8.1	256	540	23	95	41	2	1.4	9.7	16	0.01
KL34-04	151	154.9	0.0211		211	0.1	18.9	450	1240	77	108	65	2	5.3	11.8	24	0.01
KL34-04	154.9	158.8	0.004		40	0.03	6	190	480	31	40	17	1	1.1	3.7	18	0.01
KL34-04	158.8	162.1	0.063		630	0.11	24.3	5000	1600	180	71	78	3	23	13.2	29	0.11
KL34-04	162.1	164	0.078		780	0.18	28.6	2700	7100	120	126	64	8	3	8.2	29	0.01
KL34-04	164	167.1	0.048		480	0.22	6	440	870	200	360	18	6	8.3	3.8	39	0.1
KL34-04	167.1	169.9	0.0123		123	0.03	7.2	2400	1680	36	55	14	1	2.3	3.6	23	0.01
KL34-04	169.9	172.6	0.0235		235	0.04	40	10600	13400	48	33	79	1	5.2	12.3	25	0.01
KL34-04	172.6	175.1	0.0296		296	0.05	29	9700	14700	51	76	62	1	6.4	12.2	28	0.1
KL34-04	175.1	178.4	0.083		830	0.1	88	35700	41800	76	103	195	3	21	38.1	35	0.19
KL34-04	178.4	182.6	0.0198		198	0.02	26.2	5100	8200	26	56	60	1	3.5	10.6	25	0.01
KL34-04	182.6	185.8	0.0124		124	0.08	7.2	8000	3400	33	20	14	1	5.8	8.7	17	0.1
KL34-04	185.8	189.9	0.006		60	0.02	5.4	1370	1540	12	24	10	1	1.8	5.4	24	0.01
KL34-04	189.9	193.2	0.0054		54	0.01	31	5700	22400	17	5	3	2	37	4.3	11	0.16
KL34-04	193.2	196.3	0.0167		167	0.01	23	2900	26100	30	10	13	1	26	5.7	21	0.01
KL34-04	196.3	199.8	0.0054		54	0.01	3.7	880	1100	13	15	6	2	0.7	3.5	10	0.01
KL34-04	199.8	203.2	0.053		530	0.13	12.6	6450	11000	150	81	13	8	14	32.5	14	0.1
KL34-04	203.2	205.3	0.0049		49	0.02	6.3	2350	9800	8	8	3	1	7	7.1	10	0.01
KL34-04	205.3	208.2	0.0013		13	0.01	0.9	257	580	4	7	1	2	0.8	1.8	11	0.01
KL34-04	208.2	211	0.0027		27	0.01	1.6	1010	9300	5	3	1	1	0.8	2.8	8	0.01
KL34-04	211	213	0.0058		58	0.01	2	1420	1740	4	2	2	1	1.4	3.7	9	0.01
KL34-04	213	215.8	0.0031		31	0.01	1	359	294	16	14	1	1	0.9	2.6	16	0.01
KL34-04	215.8	218.8	0.0012		12	0.01	0.7	223	310	5	4	1	1	0.4	1.7	9	0.01
KL34-04	218.8	221.8	0.0029		29	0.03	2.6	2030	1160	8	5	3	1	1.4	3.1	16	0.01
KL34-04	221.8	224.8	0.0014		14	0.01	0.9	287	420	3	6	2	1	0.3	2.1	14	0.01
KL34-04	224.8	227.7	0.0043		43	0.01	0.6	319	430	5	5	1	1	0.6	2.8	12	0.01
KL34-04	227.7	230.8	0.002		20	0.01	1.3	780	760	4	3	1	1	0.7	2.9	12	0.01
KL34-04	230.8	233.8	0.0053		53	0.02	4.4	2120	1910	18	7	3	1	2.6	3.7	13	0.01
KL34-04	233.8	236.8	0.005		50	0.02	2.9	2370	600	17	45	6	3	2.3	3.4	16	0.01
KL34-04	236.8	239.8	0.0052		52	0.09	4.3	315	520	18	38	32	1	9.1	3.7	13	0.01
KL34-04	239.8	242.6	0.0028		28	0.05	1.1	1150	490	22	15	2	1	2.4	2.4	16	0.01
KL34-04	242.6	245.7	0.003		30	0.02	0.9	590	342	12	11	2	1	1.9	1.6	13	0.01
KL34-04	245.7	248.8	0.0027		27	0.01	0.7	220	285	22	26	1	1	1.9	2.3	14	0.01
KL34-04	248.8	251.8	0.0061		61	0.07	1.6	1310	520	30	13	4	1	1.5	5.0	18	0.01
KL34-04	251.8	254.8	0.0101		101	0.09	4.9	2450	1620	26	26	17	1	3.7	14.0	20	0.01
KL34-04	254.8	257.8	0.0029		29	0.04	1.3	570	352	16	11	4	1	1.1	2.5	14	0.01
KL34-04	257.8	259.9	0.0035		35	0.02	0.7	450	146	10	4	1	1	0.9	1.9	14	0.01
KL34-04	259.9	262.3	0.0046		46	0.03	0.9	136	154	11	16	3	1	0.4	1.5	14	0.01
KL34-04	262.3	265.6	0.0098		98	0.02	1.3	160	178	26	13	6	1	1.4	1.6	15	0.01
KL34-04	265.6	269.1	0.0044		44	0.02	0.9	740	420	18	21	4	1	0.8	2.5	14	0.01
KL34-04	269.1	272.1	0.0203		203	0.04	0.5	224	61	43	26	6	2	1.9	3.5	16	0.01
KL34-04	272.1	274.9	0.063		630	0.07	0.8	190	91	82	20	11	3	2.3	4.4	12	0.01
KL34-04	274.9	276.7	0.178		1780	0.36	2.5	540	278	76	7	92	15	1.5	37.4	34	0.01
KL34-04	276.7	280.4	0.0235		235	0.06	0.9	730	193	23	230	7	3	0.9	1.8	24	0.01
KL34-04	280.4	283.6	0.0201		201	0.08	0.8	103	102	18	370	4	2	0.9	2.5	31	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL34-04	283.6	287	0.0226		226	0.12	1.9	268	257	31	840	21	2	1.1	3.8	28	0.01
KL34-04	287	289.4	0.342		3420	0.27	4.2	8500	286	24	164	28	55	1.8	6.9	32	0.01
KL34-04	289.4	292.4	0.086		860	0.11	2.3	4380	205	56	4	18	7	2.5	9.3	16	0.01
KL34-04	292.4	295.7	0.58		5800	0.71	9.3	680	92	60	164	3	27	0.8	5.5	37	0.01
KL34-04	295.7	298.8	0.26		2600	0.37	10	1000	241	50	315	50	13	2.6	7.0	26	0.01
KL34-04	298.8	301.3	0.34		3400	0.22	6.6	550	102	120	85	12	21	2.6	6.3	20	0.01
KL34-04	301.3	305.2	1		10000	0.52	4.8	750	65	87	23	2	53	4.8	8.0	18	0.01
KL34-04	305.2	308.8	0.204		2040	0.24	1.9	330	166	82	13	2	13	4.2	5.5	19	0.01
KL34-04	308.8	310.8	0.501		5010	0.2	6.5	820	340	90	9	6	23	5.2	10.8	21	0.01
KL34-04	310.8	313.8	0.26		2600	0.13	2.4	5960	780	120	7	4	14	13.5	8.8	19	0.01
KL34-04	313.8	317.8	1.04		10400	0.43	17.2	4000	3100	170	150	33	20	32	8.0	38	0.01
KL34-04	317.8	320.8	0.121		1210	0.25	3.2	680	106	31	337	3	1	5.2	5.3	22	0.01
KL34-04	320.8	323.5	0.467		4670	0.47	10	3720	920	140	143	25	30	11.1	18.5	53	0.01
KL34-04	323.5	325.6	0.488		4880	0.58	6.7	6700	365	130	14	45	48	3.4	26.5	32	0.01
KL34-04	325.6	328.3	0.95		9500	0.87	4.4	8800	177	230	14	126	40	3.2	61.5	40	0.01
KL34-04	328.3	329.8	1.86		18600	1.56	4.5	4100	117	300	14	25	150	2.1	20.0	37	0.01
KL34-04	329.8	332.9	4.66		46600	1.56	6.5	940	150	490	1	4	70	4.5	15.0	33	0.01
KL34-04	332.9	335.7	3.44		34400	1.72	4.5	810	176	44	2	9	67	2.2	10.0	25	0.01
KL34-04	335.7	338.3	5.07		50700	1.86	8.6	1460	110	260	1	7	63	3.1	18.8	51	0.01
KL34-04	338.3	341.4	4.11		41100	1.88	8.9	1480	630	350	47	3	34	6	19.0	57	0.01
KL34-04	341.4	344.1	2.97		29700	0.72	16	2010	710	170	72	4	27	114	22.5	105	0.2
KL34-04	344.1	347	1.62		16200	0.14	6.7	830	460	270	291	2	17	60	14.5	86	0.35
KL34-04	347	350	0.95		9500	0.08	1	205	121	13	54	0.01	14	1.2	15.5	54	0.11
KL34-04	350	353.1	1.37		13700	0.11	3	790	430	110	182	0.01	13	9.7	12.8	112	0.35
KL34-04	353.1	356.2	0.56		5600	0.15	8.9	740	540	76	39	2	12	18.2	6.5	93	0.01
KL34-04	356.2	359.3	1.32		13200	0.25	4.3	209	103	57	59	1	23	11.8	13.6	48	0.1
KL34-04	359.3	362.3	1.07		10700	0.44	5.9	312	158	33	28	1	11	7	8.0	86	0.01
KL34-04	362.3	365.4	1.25		12500	0.5	7.2	103	64	16	15	5	11	5.3	4.8	76	0.1
KL34-04	365.4	368.5	0.58		5800	0.21	5	364	269	12	29	3	9	7.4	6.0	38	0.01
KL34-04	368.5	371.6	0.93		9300	0.21	2.8	560	335	120	62	2	13	14.3	10.0	59	0.13
KL34-04	371.6	374.7	0.67		6700	0.14	1.9	99	30	10	47	1	7	0.3	5.1	49	0.1
KL34-04	374.7	377.7	0.501		5010	0.14	1.4	350	54	8	32	1	8	1.9	3.8	89	0.1
KL34-04	377.7	380.7	0.384		3840	0.06	1.7	172	73	20	50	1	6	2.7	5.3	67	0.01
KL34-04	380.7	383.7	0.57		5700	0.14	2.9	470	2760	25	73	1	8	4.5	7.5	68	0.01
KL34-04	383.7	386.7	0.364		3640	0.11	1.1	349	133	12	281	1	8	2.5	4.9	62	0.01
KL34-04	386.7	389.7	0.58		5800	0.23	2	166	91	5	42	2	9	2	4.5	53	0.01
KL34-04	389.7	392.7	1.18		11800	0.1	4.2	530	330	180	420	1	9	50	7.5	48	0.01
KL34-04	392.7	395.7	0.9		9000	0.16	3.8	480	259	42	64	3	7	11	14.8	40	0.1
KL34-04	395.7	398.4	1.65		16500	0.27	8.9	97	113	21	301	3	10	25	8.0	76	0.21
KL34-04	398.4	401.5	1.37		13700	0.38	6.1	21	86	17	83	42	9	23	8.0	47	0.18
KL34-04	401.5	404.6	1.04		10400	0.84	12.9	22	170	58	36	10	7	35	8.0	60	0.33
KL34-04	404.6	407.7	4.52		45200	3.55	71	42	184	2200	151	9	4	112	6.0	152	1.32
KL34-04	407.7	410.7	0.6		6000	0.37	12	44	650	340	106	10	4	44	5.8	147	0.12
KL34-04	410.7	413.7	0.6		6000	0.21	0.8	73	221	100	177	5	7	5	6.0	113	0.01
KL34-04	413.7	416.7	0.359		3590	0.04	0.7	33	43	10	94	0.01	4	1.2	3.3	224	0.01
KL34-04	416.7	419.7	0.402		4020	0.02	0.6	29	22	8	65	0.01	3	0.9	3.5	193	0.01
KL34-04	419.7	422.9	0.307		3070	0.02	0.6	28	19	3	41	0.01	2	0.2	2.9	145	0.01
KL34-04	422.9	425.7	0.39		3900	0.04	1.1	93	81	43	60	0.01	5	2.8	4.5	113	0.01
KL34-04	425.7	428.7	0.32		3200	0.08	1.1	90	74	25	158	0.01	7	3.2	3.8	155	0.01
KL34-04	428.7	431.7	0.38		3800	0.11	1.6	149	189	51	154	0.01	7	3.1	5.3	143	0.01
KL34-04	431.7	434.7	0.51		5100	0.15	1.7	138	123	140	56	1	6	22	3.5	193	0.01
KL34-04	434.7	437.7	0.98		9800	0.22	2.3	43	50	100	355	0.01	8	2.2	5.5	110	0.01
KL34-04	437.7	440.7	1.17		11700	0.27	2.3	720	250	54	64	3	4	8.4	3.3	98	0.01
KL34-04	440.7	443.7	0.496		4960	0.04	1.7	130	65	42	44	1	4	46	3.3	117	0.01
KL34-04	443.7	446.7	0.55		5500	0.05	0.1	48	35	20	66	0.01	7	6.3	3.8	99	0.01
KL34-04	446.7	449.7	0.96		9600	0.21	1.7	77	46	38	44	2	6	5.5	6.1	119	0.01
KL34-04	449.7	452.7	0.488		4880	0.05	0.9	197	74	45	52	0.01	4	2.7	4.0	129	0.01
KL34-04	452.7	455.7	0.0107		107	0.01	0.1	61	19	2	2	0.01	15	0.01	0.0	26	0.01
KL34-04	455.7	458.3	0.32		3200	0.11	1.1	1650	530	92	50	1	3	4.6	3.8	190	0.01
KL34-04	458.3	461.4	0.34		3400	0.87	2.2	10400	1530	39	52	2	3	1	3.3	130	0.28
KL34-04	461.4	464.5	0.6		6000	0.16	1.2	90	24	9	22	0.01	7	0.4	3.0	178	0.01
KL34-04	464.5	467.6	0.53		5300	0.11	0.5	84	25	2	49	0.01	5	0.2	3.8	200	0.01
KL34-04	467.6	470.6	0.54		5400	0.19	0.6	39	12	1	21	0.01	6	0.01	3.8	140	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL34-04	470.6	473.7	0.84	8400	0.31	0.9	127	27	3	22	1	8	0.01	3.1	282	0.01
KL34-04	473.7	476.7	0.449	4490	0.12	0.8	202	73	4	36	0.01	4	0.4	2.5	159	0.01
KL34-04	476.7	479.7	0.5	5000	0.18	0.7	47	21	3	28	0.01	7	0.3	2.0	118	0.01
KL34-04	479.7	482.7	0.448	4480	0.12	1.5	93	46	4	30	1	6	2.9	3.0	208	0.01
KL34-04	482.7	485.7	0.83	8300	0.2	19.7	600	199	90	52	16	5	146	5.5	124	0.27
KL34-04	485.7	488.7	0.51	5100	0.14	0.8	119	51	14	69	0.01	4	16.8	3.8	226	0.01
KL34-04	488.7	491.7	1.24	12400	0.29	0.1	95	25	440	58	0.01	4	0.5	5.8	276	0.01
KL34-04	491.7	494.7	0.409	4090	0.13	0.1	23	13	36	78	0.01	6	0.2	2.5	167	0.01
KL34-04	494.7	497.7	0.57	5700	0.19	0.7	35	27	6	24	1	9	0.01	3.8	150	0.01
KL34-04	497.7	500.7	0.423	4230	0.19	0.6	840	151	12	38	0.01	5	5.6	3.4	271	0.1
KL34-04	500.7	503.7	0.51	5100	0.1	0.7	22	15	350	114	0.01	10	2	2.8	189	0.01
KL34-04	503.7	506.7	0.68	6800	0.12	0.7	12	8	410	39	0.01	7	3.2	2.8	98	0.01
KL34-04	506.7	508.8	0.55	5500	0.09	0.9	77	86	350	23	1	5	1	7.5	49	0.01
KL34-04	508.8	511.8	0.59	5900	0.1	1.4	60	51	240	33	1	6	2.5	5.5	81	0.01
KL34-04	511.8	514.9	0.63	6300	0.07	1	48	22	370	34	0.01	8	1.2	5.7	106	0.01
KL34-04	514.9	518.7	0.481	4810	0.11	2.7	242	182	23	44	2	8	75	5.0	74	0.01
KL34-04	518.7	521.7	0.57	5700	0.23	1.3	84	36	15	38	1	8	1	6.3	68	0.01
KL34-04	521.7	524.7	0.7	7000	0.07	2.9	370	178	71	27	2	5	6	7.7	63	0.1
KL34-04	524.7	527.7	0.78	7800	0.11	3.4	304	155	120	42	2	5	11.8	5.5	42	0.01
KL34-04	527.7	530.7	1.78	17800	0.25	15.1	5900	1100	260	31	11	5	50	7.3	43	0.48
KL34-04	530.7	533.7	0.72	7200	0.14	3.8	148	166	1060	63	1	4	17.4	7.0	57	0.1
KL34-04	533.7	536.7	0.98	9800	0.15	2.1	145	78	2040	110	1	5	8.9	6.2	82	0.1
KL34-04	536.7	539.7	0.78	7800	0.28	2.4	184	65	1340	48	1	6	4.7	5.8	46	0.01
KL34-04	539.7	542.7	0.407	4070	0.39	1.3	100	54	18	42	1	7	0.4	3.3	53	0.01
KL34-04	542.7	545.7	0.369	3690	0.1	1.2	74	29	18	36	1	4	0.2	3.3	50	0.01
KL34-04	545.7	548.7	0.509	5090	0.19	1.3	73	30	13	31	1	6	0.01	4.0	49	0.01
KL34-04	548.7	551.7	0.52	5200	0.19	2	72	24	16	25	1	7	0.2	6.0	53	0.01
KL34-04	551.7	554.7	0.498	4980	0.14	1.5	194	122	50	29	1	6	5.4	5.2	103	0.01
KL34-04	554.7	557.7	0.473	4730	0.16	2.2	150	69	8	34	1	7	0.5	3.2	58	0.01
KL34-04	557.7	560.7	0.66	6600	0.18	3.6	273	112	20	44	2	5	3.4	4.7	68	0.01
KL34-04	560.7	563.7	0.57	5700	0.16	5.3	410	430	37	36	2	8	205	6.8	47	0.01
KL34-04	563.7	566.7	0.354	3540	0.09	2.6	61	35	5	20	1	6	3.5	3.5	98	0.01
KL34-04	566.7	569.5	0.384	3840	0.08	1.8	73	28	9	38	1	7	9.6	4.0	90	0.01
KL34-04	569.5	572.7	0.379	3790	0.06	1.2	95	82	28	34	1	6	5.8	4.0	151	0.01
KL34-04	572.7	575.7	0.21	2100	0.04	0.6	74	51	12	14	0.01	3	3.7	2.5	90	0.01
KL34-04	575.7	578.7	0.314	3140	0.05	0.8	73	44	14	23	0.01	6	3.9	3.2	191	0.01
KL34-04	578.7	581.7	0.28	2800	0.07	0.8	138	72	38	48	1	5	0.5	2.8	106	0.01
KL34-04	581.7	584.7	0.25	2500	0.07	1.4	183	105	210	97	5	4	6.5	4.9	136	0.01
KL34-04	584.7	587.7	0.291	2910	0.03	0.7	57	27	15	30	1	5	0.3	3.5	88	0.01
KL34-04	587.7	590.7	0.27	2700	0.02	0.8	203	95	27	34	1	6	1.1	4.1	126	0.01
KL34-04	590.7	593.7	0.285	2850	0.07	1.7	103	83	20	45	2	6	12.1	3.8	84	0.01
KL34-04	593.7	596.7	0.22	2200	0.04	0.6	117	75	12	54	0.01	3	3.1	2.7	63	0.01
KL34-04	596.7	599.7	0.21	2100	0.03	0.5	45	21	13	33	1	2	0.3	2.8	81	0.01
KL34-04	599.7	602.7	0.23	2300	0.02	0.5	31	13	4	52	0.01	3	0.01	3.0	140	0.01
KL34-04	602.7	605.7	0.331	3310	0.03	1	86	55	28	28	1	4	1.9	3.3	86	0.01
KL34-04	605.7	608.7	0.26	2600	0.03	0.9	93	89	14	30	1	5	1.6	2.8	136	0.01
KL34-04	608.7	611.7	0.23	2300	0.03	0.6	74	33	10	37	0.01	4	0.6	2.8	92	0.01
KL34-04	611.7	614.7	0.21	2100	0.08	1	75	42	24	76	0.01	3	1.9	2.5	179	0.01
KL34-04	614.7	617.7	0.21	2100	0.07	1	259	131	15	57	1	4	2.5	3.2	133	0.01
KL34-04	617.7	620.7	0.383	3830	0.05	3.6	100	116	240	91	6	5	32	3.8	65	0.01
KL34-04	620.7	623.7	0.2	2000	0.03	1.4	65	108	160	88	2	4	7.8	4.0	72	0.01
KL34-04	623.7	626.7	0.427	4270	0.13	2.6	244	287	1320	118	3	5	21.5	3.5	61	0.01
KL34-04	626.7	629.7	0.19	1900	0.01	0.5	169	168	81	116	0.01	4	1	3.0	116	0.01
KL34-04	629.7	632.7	0.23	2300	0.02	0.8	170	130	370	52	1	4	7.1	3.3	174	0.01
KL34-04	632.7	635.7	0.196	1960	0.02	0.1	18	11	30	103	0.01	4	0.5	1.6	183	0.01
KL34-04	635.7	638.7	0.187	1870	0.02	0.1	23	16	7	81	0.01	4	1.4	2.0	135	0.01
KL34-04	638.7	641.7	0.16	1600	0.03	0.1	18	9	13	30	0.01	3	0.01	2.2	140	0.01
KL34-04	641.7	644.7	0.23	2300	0.03	0.1	16	18	4	71	0.01	4	0.01	2.9	155	0.01
KL34-04	644.7	647.7	0.2	2000	0.02	0.1	15	7	1	91	0.01	3	0.01	2.2	105	0.01
KL34-04	647.7	650.7	0.147	1470	0.01	0.1	38	30	5	40	10	3	0.4	2.2	61	0.01
KL34-04	650.7	653.7	0.16	1600	0.01	0.1	24	15	5	76	0.01	3	1	2.0	60	0.01
KL34-04	653.7	656.7	0.162	1620	0.01	0.1	47	25	4	86	0.01	2	0.9	1.5	78	0.01
KL34-04	656.7	659.7	0.195	1950	0.01	0.5	79	127	4	1100	0.01	2	0.6	3.2	58	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL34-04	659.7	662.7	0.171	1710	0.01	0.1	43	23	6	39	0.01	5	0.8	2.0	60	0.01
KL34-04	662.7	665.7	0.192	1920	0.01	0.8	29	18	12	35	0.01	4	1	2.1	57	0.01
KL34-04	665.7	668.7	0.114	1140	0.01	0.1	75	43	15	55	0.01	3	0.5	0.5	145	0.01
KL34-04	668.7	671.7	0.128	1280	0.01	0.8	73	163	18	160	0.01	3	0.5	1.2	205	0.01
KL34-04	671.7	674.7	0.118	1180	0.01	0.1	44	38	170	53	0.01	2	4.5	1.2	117	0.01
KL34-04	674.7	677.7	0.132	1320	0.01	0.9	58	107	310	37	2	3	3	1.0	193	0.01
KL34-04	677.7	680.7	0.142	1420	0.03	1.1	196	162	140	45	9	3	2.4	1.3	187	0.01
KL34-04	680.7	683.7	0.153	1530	0.01	2.3	109	126	6	75	1	4	3	0.7	147	0.01
KL34-04	683.7	686.7	0.2	2000	0.02	1.9	70	53	3	44	0.01	4	0.5	2.0	204	0.01
KL34-04	686.7	689.7	0.168	1680	0.02	0.8	39	28	5	48	0.01	4	1.2	2.0	230	0.01
KL34-04	689.7	692.7	0.23	2300	0.09	0.8	11	8	1	89	0.01	2	0.2	2.5	140	0.01
KL34-04	692.7	695.7	0.207	2070	0.06	1.6	24	21	2	65	0.01	4	0.2	2.2	171	0.01
KL34-04	695.7	698.7	0.21	2100	0.04	0.5	112	56	4	28	0.01	5	0.01	1.8	173	0.01
KL34-04	698.7	701.7	0.19	1900	0.01	0.9	89	50	4	83	1	5	1.5	2.8	230	0.01
KL34-04	701.7	704.7	0.21	2100	0.03	1.1	73	37	3	72	0.01	7	0.2	1.8	140	0.01
KL34-04	704.7	707.7	0.285	2850	0.04	0.8	78	60	130	81	0.01	8	2.7	3.2	231	0.01
KL34-04	707.7	710.7	0.193	1930	0.01	0.7	41	51	3	49	0.01	5	0.01	3.3	127	0.01
KL34-04	710.7	714.6	0.197	1970	0.01	0.8	27	20	11	57	0.01	6	0.2	2.2	172	0.01
KL34-04	714.6	719.7	0.2	2000	0.02	0.5	24	15	2	58	1	5	0.01	2.2	112	0.01
KL34-04	719.7	722.7	0.23	2300	0.07	4.1	88	96	390	79	6	5	4.4	7.5	180	0.21
KL34-04	722.7	725.7	0.2	2000	0.03	1.3	75	83	27	34	0.01	6	0.5	3.0	132	0.01
KL34-04	725.7	728.7	0.249	2490	0.06	1.3	60	53	15	27	1	6	0.8	3.2	114	0.01
KL34-04	728.7	731.7	0.195	1950	0.05	1.3	44	37	26	17	2	6	0.4	2.5	161	0.01
KL34-04	731.7	734.7	0.188	1880	0.03	1.5	111	36	110	27	18	4	3.9	2.0	104	0.01
KL34-05	0	5.2	0.0033	33	0.04	1	350	127	13	1	0.01	1	0.8	1.8	16	0.01
KL34-05	5.2	8.7	0.0085	85	0.02	0.8	314	129	11	3	0.01	1	1	1.8	22	0.01
KL34-05	8.7	11	0.0039	39	0.02	1.2	730	205	23	3	0.01	1	1.3	1.5	21	0.01
KL34-05	11	14.1	0.0035	35	0.02	1.3	398	125	19	3	0.01	1	0.8	1.8	20	0.01
KL34-05	14.1	17.2	0.005	50	0.02	1.1	910	290	17	3	0.01	1	1.1	2.0	25	0.01
KL34-05	17.2	20.7	0.0064	64	0.02	1.6	1410	386	23	2	0.01	1	1.3	1.5	23	0.01
KL34-05	20.7	23.7	0.0025	25	0.03	1.2	710	660	21	3	0.01	1	1.3	3.3	20	0.01
KL34-05	23.7	26.7	0.003	30	0.05	1.3	920	430	16	2	0.01	1	1.3	2.8	21	0.01
KL34-05	26.7	29.7	0.0182	182	0.01	10.9	5100	7600	41	13	8	1	5.1	32.4	24	0.01
KL34-05	29.7	32.7	0.0031	31	0.02	1.7	590	880	13	3	1	1	1.4	4.8	23	0.01
KL34-05	32.7	35.7	0.0112	112	0.04	0.9	409	310	28	12	1	2	1.3	4.0	43	0.01
KL34-05	35.7	38.7	0.0221	221	0.04	12.5	6500	9700	58	13	11	2	7.3	36.2	27	0.01
KL34-05	38.7	41.3	0.0029	29	0.03	1	560	820	18	3	0.01	1	1.4	2.5	25	0.01
KL34-05	41.3	43.5	0.0084	84	0.09	3.2	2400	2410	30	5	1	1	5.3	6.0	19	0.01
KL34-05	43.5	46.5	0.0037	37	0.04	1.2	640	780	22	3	1	1	2	2.3	26	0.01
KL34-05	46.5	50.7	0.0025	25	0.05	0.5	540	249	23	2	0.01	1	1	2.5	21	0.01
KL34-05	50.7	53.7	0.0262	262	0.04	0.7	930	327	38	15	3	2	2.7	2.5	77	0.01
KL34-05	53.7	56.7	0.0038	38	0.01	0.7	358	235	18	8	2	1	1.1	2.3	36	0.01
KL34-05	56.7	59.7	0.011	110	0.03	2.5	1080	840	24	4	0.01	1	3.5	2.3	50	0.01
KL34-05	59.7	62.7	0.0224	224	0.03	1.8	1130	590	44	9	2	2	3.6	3.5	74	0.01
KL34-05	62.7	65.7	0.0091	91	0.04	0.1	352	160	25	15	1	2	1.5	2.5	39	0.01
KL34-05	65.7	68.7	0.0155	155	0.02	1.1	310	148	17	4	1	2	1.2	2.8	25	0.01
KL34-05	68.7	71.7	0.0046	46	0.11	2.3	2590	1520	19	3	3	1	5.8	6.5	19	0.16
KL34-05	71.7	74.6	0.012	120	0.78	6.7	6600	2140	84	3	14	1	15.8	17.1	26	0.45
KL34-05	74.6	77.7	0.0372	372	0.11	3.3	290	1170	130	6	6	1	28	4.3	102	0.1
KL34-05	77.7	80.7	0.09	900	0.58	14.7	1570	940	280	7	62	2	18.1	14.6	136	0.28
KL34-05	80.7	84.7	0.041	410	0.11	3.3	1650	750	91	7	7	1	13	4.5	53	0.16
KL34-05	84.7	86.3	0.0163	163	0.12	4.5	660	2350	31	7	8	1	3.8	3.3	28	0.01
KL34-05	86.3	90.1	0.014	140	0.15	7.1	1210	1460	40	5	12	1	3.7	7.0	164	0.01
KL34-05	90.1	93.1	0.121	1210	0.18	51	3700	19600	310	14	67	1	40	15.8	44	0.26
KL34-05	93.1	96.8	0.12	1200	0.39	31.3	3700	7500	420	12	35	1	26	14.0	159	0.14
KL34-05	96.8	98.7	0.168	1680	0.42	56	11400	9700	550	16	111	3	32	14.6	165	0.45
KL34-05	98.7	101.1	0.175	1750	0.4	19.8	4910	3190	550	25	60	2	23	7.8	107	0.32
KL34-05	101.1	103.7	0.155	1550	0.23	13.6	2360	2440	500	96	48	1	17.7	11.5	102	0.18
KL34-05	103.7	107.7	0.191	1910	0.38	13.3	3960	2510	510	209	28	1	30	11.0	105	0.37
KL34-05	107.7	110.7	0.0112	112	0.28	3.2	2670	790	58	8	5	1	6.4	4.8	30	0.18
KL34-05	110.7	113.9	0.0076	76	0.13	3.8	2060	1820	34	9	9	1	4.2	7.8	25	0.01
KL34-05	113.9	116	0.0089	89	0.15	3.9	2700	2600	29	10	5	1	3.9	10.0	20	0.13
KL34-05	116	118.4	0.0084	84	0.07	3.7	1730	1390	21	7	8	1	4.4	6.3	21	0.1

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL34-05	118.4	122	0.0075		75	0.15	3.2	1900	910	26	10	9	1	6.8	7.6	26	0.1
KL34-05	122	125	0.0045		45	0.15	4.8	2030	1340	43	9	13	1	3.9	7.8	25	0.01
KL34-05	125	128.7	0.0061		61	0.15	8.4	4160	3690	33	13	18	1	5.5	10.5	26	0.01
KL34-05	128.7	130.9	0.0041		41	0.08	5.5	780	960	23	13	10	1	6.8	5.3	31	0.01
KL34-05	130.9	133.7	0.0035		35	0.09	2.3	670	303	25	11	6	1	3.2	2.5	28	0.01
KL34-05	133.7	137.7	0.0086		86	0.08	8.7	2950	3020	24	17	13	2	3.7	9.3	28	0.01
KL34-05	137.7	140.7	0.0132		132	0.11	29	4200	6900	41	23	50	1	11.8	18.2	29	0.01
KL34-05	140.7	143.3	0.0107		107	0.1	21.7	2920	5900	32	25	39	1	13	13.0	30	0.01
KL34-05	143.3	146.7	0.0246		246	0.09	15	8400	5200	40	22	30	1	7.3	12.8	21	0.01
KL34-05	146.7	149.7	0.004		40	0.06	3.3	2960	2710	25	21	1	1	4.1	3.5	21	0.01
KL34-05	149.7	152.4	0.0039		39	0.06	3.1	1050	1070	12	17	5	1	1.6	3.7	16	0.01
KL34-05	152.4	155.5	0.0092		92	0.1	10.3	2910	3840	26	39	18	1	5.3	7.3	19	0.01
KL34-05	155.5	158.6	0.0174		174	0.11	11.5	3450	3130	34	37	14	1	4.1	8.8	19	0.01
KL34-05	158.6	161.7	0.0065		65	0.07	6.6	1950	3060	18	39	12	1	5.1	4.8	20	0.01
KL34-05	161.7	164.7	0.0338		338	0.11	6	2610	2540	30	37	14	1	2	13.6	22	0.01
KL34-05	164.7	168.9	0.0107		107	0.05	4.1	1750	2050	28	36	4	1	2.5	6.3	19	0.01
KL34-05	168.9	173.3	0.007		70	0.05	5.4	2690	2670	28	34	2	1	4.6	4.5	20	0.01
KL34-05	173.3	176.7	0.0043		43	0.07	5.2	1060	700	22	21	7	1	4.3	3.8	22	0.01
KL34-05	176.7	179.4	0.0208		208	0.1	13.5	6700	9300	75	77	10	1	13.7	11.3	20	0.01
KL34-05	179.4	182.7	0.051		510	0.16	14.7	12400	6600	160	131	9	1	14	13.0	18	0.1
KL34-05	182.7	185.7	0.098		980	0.19	30.3	28800	16800	280	280	18	1	28	23.9	17	0.15
KL34-05	185.7	188.7	0.022		220	0.13	15	8800	6600	72	72	9	1	14.5	16.8	17	0.1
KL34-05	188.7	191.7	0.0193		193	0.08	12.8	5500	10600	61	87	4	1	15.6	9.0	28	0.01
KL34-05	191.7	194.7	0.0067		67	0.07	5.8	6200	3470	43	34	4	1	7.3	7.0	24	0.01
KL34-05	194.7	197.7	0.0116		116	0.21	5.9	3230	2090	53	26	4	1	8.3	7.6	21	0.01
KL34-05	197.7	200.7	0.0086		86	0.09	7.6	5900	2910	41	16	2	1	11	5.3	18	0.01
KL34-05	200.7	203.7	0.0103		103	0.19	4.8	3270	2600	45	28	4	1	5.4	8.3	18	0.01
KL34-05	203.7	206	0.084		840	0.14	34.5	32300	18600	230	210	17	4	34	18.6	18	0.01
KL34-05	206	209	0.067		670	0.64	33.2	27300	28700	220	71	11	1	48	30.9	17	0.4
KL34-05	209	212	0.053		530	0.17	6.4	3860	1840	40	36	19	3	3.8	7.0	24	0.01
KL34-05	212	215.7	0.195		1950	0.22	8.5	1980	2450	39	58	16	4	2.8	19.0	20	0.01
KL34-05	215.7	218.7	0.0475		475	0.14	6.9	6500	3520	42	36	8	1	7.5	8.0	30	0.01
KL34-05	218.7	221.7	0.073		730	0.15	5.5	1170	1170	30	44	10	1	3.3	10.0	21	0.01
KL34-05	221.7	224.6	0.77		7700	0.74	13.4	161	250	31	32	18	40	6.4	30.8	40	0.01
KL34-05	224.6	227.7	0.78		7800	0.8	21.4	700	149	36	187	57	31	7.1	33.2	45	0.01
KL34-05	227.7	230.7	0.401		4010	0.48	4.8	221	134	35	1750	38	21	2.2	52.0	86	0.01
KL34-05	230.7	233.7	0.447		4470	0.64	16.7	400	358	52	1020	197	20	3.3	61.0	68	0.01
KL34-05	233.7	236.7	0.153		1530	0.66	5.9	5750	890	110	980	35	15	17.1	24.2	116	0.41
KL34-05	236.7	239.7	1.24		12400	1.25	19.8	1540	350	63	180	15	52	6	19.0	54	0.1
KL34-05	239.7	242.7	1.37		13700	0.96	30.7	366	118	24	25	45	38	4	15.4	34	0.01
KL34-05	242.7	245.7	0.54		5400	0.52	12.9	5300	249	44	58	22	56	3.2	13.3	85	0.01
KL34-05	245.7	248.5	0.62		6200	0.44	13.1	4760	149	37	72	20	17	3.8	17.8	43	0.01
KL34-05	248.5	251.7	0.8		8000	0.63	21.3	6300	140	25	22	13	9	4.4	8.5	27	0.01
KL34-05	251.7	254.7	0.175		1750	0.32	7	1520	110	54	106	25	11	7.9	7.3	41	0.01
KL34-05	254.7	260.4	0.71		7100	0.63	19.9	3280	263	71	56	10	30	5.2	9.0	43	0.01
KL34-05	260.4	263.7	0.455		4550	0.35	12.6	6650	2530	90	179	26	33	5.6	9.7	36	0.01
KL34-05	263.7	266.7	1.01		10100	2.19	15	930	368	50	105	70	47	3.1	15.2	38	0.01
KL34-05	266.7	269.7	0.88		8800	1.29	23.4	1220	500	54	184	182	12	3	8.0	28	0.01
KL34-05	269.7	272.8	0.82		8200	2.44	10	440	291	30	170	32	22	3.3	13.0	53	0.01
KL34-05	272.8	274.9	2.99		29900	2.48	31	3400	580	87	86	74	22	14	11.5	92	0.15
KL34-05	274.9	277.8	1.61		16100	2.06	29.2	5900	1900	510	75	27	47	285	18.9	58	0.37
KL34-05	277.8	280.8	0.98		9800	1.74	14.8	1640	500	200	3	30	48	6.8	10.3	61	0.11
KL34-05	280.8	284.7	1.14		11400	2.12	13	4300	236	37	17	54	31	6.7	11.3	90	0.01
KL34-05	284.7	287.7	0.68		6800	2.16	18.5	4400	8100	39	6	53	15	3.6	25.3	48	0.18
KL34-05	287.7	290.7	0.99		9900	2.14	125	5000	2700	490	5	54	32	39	13.0	45	0.44
KL34-05	290.7	293.7	1.86		18600	3.04	5.1	302	240	45	7	18	28	1.5	11.8	86	0.01
KL34-05	293.7	296.7	1.74		17400	1.88	2.9	145	82	36	1	9	72	5.2	19.5	49	0.01
KL34-05	296.7	299.7	2.28		22800	4	8.1	286	306	710	35	8	73	6	38.0	95	0.25
KL34-05	299.7	302.7	2.89		28900	2.32	9.3	180	205	370	15	20	18	3.1	56.0	54	0.23
KL34-05	302.7	305.7	1.96		19600	2.44	5.3	395	610	130	1	8	41	2.4	26.5	74	0.19
KL34-05	305.7	308.5	2.08		20800	2.7	9.5	690	389	500	1	8	34	2.7	24.5	65	0.26
KL34-05	308.5	311.5	2.64		26400	3.72	14.1	1590	840	620	10	14	48	2.6	49.0	68	0.29
KL34-05	311.5	314.7	1.36		13600	1.22	10	1060	640	510	1020	149	72	5.6	65.0	54	0.18

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL34-05	314.7	317.7	1.21	12100	0.43	3.5	2700	319	160	251	12	45	1	42.5	90	0.2
KL34-05	317.7	320.7	0.7	7000	0.21	2.2	3940	900	620	357	3	30	3.2	19.0	154	0.65
KL34-05	320.7	323.7	1.5	15000	0.41	4.3	3000	820	590	159	7	34	2.2	16.8	108	0.72
KL34-05	323.7	326.7	0.84	8400	0.23	2.7	5100	3060	570	251	3	25	2.7	17.5	134	0.99
KL34-05	326.7	329.7	0.68	6800	0.33	2.1	265	88	39	302	0.01	45	0.5	13.5	61	0.15
KL34-05	329.7	332.7	1.22	12200	0.2	2.7	391	150	98	242	1	67	0.5	14.3	100	0.2
KL34-05	332.7	335.7	0.478	4780	0.27	1.1	192	50	63	186	0.01	31	0.2	11.0	88	0.01
KL34-05	335.7	338.7	0.39	3900	0.23	1.4	910	1330	39	317	0.01	18	0.3	11.0	82	0.28
KL34-05	338.7	341.7	1.51	15100	0.52	2.8	175	40	6	145	0.01	36	0.01	11.5	63	0.01
KL34-05	341.7	344.7	1.34	13400	0.53	2.9	360	54	36	487	0.01	29	0.3	12.8	77	0.01
KL34-05	344.7	347.7	1.24	12400	0.21	2.4	54	21	23	630	0.01	28	0.01	11.0	50	0.01
KL34-05	347.7	350.7	0.93	9300	0.28	2.8	43	30	15	496	1	44	0.01	12.3	48	0.01
KL34-05	350.7	353.7	0.86	8600	0.27	1.4	62	31	11	490	0.01	20	0.01	10.2	72	0.01
KL34-05	353.7	356.7	1.73	17300	0.31	2.7	171	60	72	281	3	54	5.3	13.5	48	0.01
KL34-05	356.7	359.7	1.22	12200	0.14	2.5	107	59	6	520	0.01	28	0.01	12.5	39	0.01
KL34-05	359.7	362.7	0.63	6300	0.19	1.3	154	38	19	251	3	14	1.5	9.0	55	0.01
KL34-05	362.7	365.7	0.99	9900	0.36	2.3	710	197	120	321	8	17	12.5	10.3	43	0.28
KL34-05	365.7	368.7	1.03	10300	0.3	1.6	151	149	37	390	1	32	0.01	8.5	45	0.1
KL34-05	368.7	371.7	1.25	12500	0.42	1.8	67	28	24	270	0.01	17	0.01	8.5	70	0.01
KL34-05	371.7	374.7	1.51	15100	0.37	2.1	62	15	5	550	1	19	0.01	8.0	61	0.01
KL34-05	374.7	377.7	2.17	21700	0.66	2.8	28	6	5	670	1	18	0.01	9.0	77	0.01
KL34-05	377.7	380.7	2.77	27700	0.97	2.2	46	8	29	530	1	19	0.01	15.0	81	0.01
KL34-05	380.7	383.7	1.68	16800	0.61	2.3	41	15	4	660	1	16	0.01	11.0	57	0.01
KL34-05	383.7	386.7	1.67	16700	0.53	2.7	261	60	30	640	0.01	15	0.01	9.5	70	0.01
KL34-05	386.7	390.1	2.03	20300	0.69	3.8	127	139	1310	850	3	19	22	7.5	56	0.55
KL34-05	390.1	394.6	3.04	30400	1.36	3.9	241	67	130	1180	1	20	4.7	14.0	89	0.26
KL34-05	394.6	396.7	6.93	69300	2.05	5.4	135	20	8	710	1	31	0.01	18.8	104	0.01
KL34-05	396.7	400	3.4	34000	1.21	3.7	100	8	3	1540	0.01	33	0.01	10.0	107	0.01
KL34-05	400	402.7	1.65	16500	0.36	2.4	63	7	8	940	0.01	12	0.01	7.5	130	0.01
KL34-05	402.7	404.7	0.88	8800	0.26	1.6	25	5	2	460	0.01	6	0.4	4.8	152	0.01
KL34-05	404.7	407.7	1.17	11700	0.25	2.1	67	30	16	680	0.01	7	0.6	5.8	185	0.01
KL34-05	407.7	410.7	0.87	8700	0.21	1.9	40	13	16	470	0.01	10	0.4	6.3	163	0.01
KL34-05	410.7	413.5	0.44	4400	0.15	1.1	26	8	3	280	0.01	12	0.01	6.3	166	0.01
KL34-05	413.5	416.6	0.46	4600	0.14	1.2	169	50	11	229	0.01	18	0.2	9.1	141	0.01
KL34-05	416.6	419.7	0.94	9400	0.33	2.1	338	135	61	284	1	17	14.5	8.8	167	0.01
KL34-05	419.7	422.7	1.2	12000	0.33	1.6	135	40	48	171	1	8	0.9	11.5	149	0.01
KL34-05	422.7	425.7	0.31	3100	0.08	0.8	20	7	3	237	0.01	9	0.01	6.8	171	0.01
KL34-05	425.7	428.7	0.32	3200	0.1	0.8	18	5	2	295	0.01	10	0.01	9.6	153	0.01
KL34-05	428.7	431.7	0.47	4700	0.17	1.2	170	138	82	297	0.01	20	5.4	11.8	117	0.01
KL34-05	431.7	434.7	0.49	4900	0.18	0.8	135	37	19	1330	0.01	10	0.01	7.5	130	0.01
KL34-05	434.7	437.7	0.7	7000	0.23	0.9	199	39	15	159	1	12	0.5	11.0	99	0.01
KL34-05	437.7	440.7	0.61	6100	0.15	1.6	410	362	310	660	1	4	0.5	9.0	108	0.01
KL34-05	440.7	443.7	0.45	4500	0.1	0.1	22	11	3	333	0.01	8	0.01	5.5	152	0.01
KL34-05	443.7	445.9	0.42	4200	0.1	0.8	96	112	550	261	0.01	2	0.6	7.0	132	0.01
KL34-05	445.9	448.7	0.33	3300	0.11	1.1	124	52	700	264	0.01	8	1	6.3	145	0.01
KL34-05	448.7	451.7	0.65	6500	0.1	2.6	150	43	12	259	1	7	0.5	7.3	181	0.01
KL34-05	451.7	454.7	1.04	10400	0.13	3.9	93	42	33	560	2	16	0.01	12.0	169	0.01
KL34-05	454.7	457.8	1.31	13100	0.25	4	430	470	140	329	2	15	4.5	12.5	156	0.15
KL34-05	457.8	461.1	1.04	10400	0.15	2.8	47	26	22	560	2	14	0.6	11.5	163	0.01
KL34-05	461.1	464.2	1.09	10900	0.68	3.7	880	112	15	415	2	35	0.2	14.0	157	0.01
KL34-05	464.2	468.1	1.72	17200	0.68	6.9	193	54	7	670	2	42	0.01	30.3	192	0.01
KL34-05	468.1	470.3	1.07	10700	0.6	3.7	98	12	1	32	1	41	0.01	34.0	87	0.01
KL34-05	470.3	473.4	1.44	14400	0.64	3.2	123	11	1	44	0.01	48	0.01	17.0	36	0.01
KL34-05	473.4	476.5	1.06	10600	0.47	2.2	81	12	0.01	27	0.01	39	0.01	10.5	27	0.01
KL34-05	476.5	479.6	0.54	5400	0.21	1.4	67	7	0.01	19	1	29	0.01	12.8	21	0.01
KL34-05	479.6	482.6	0.97	9700	0.41	7.6	99	181	1	24	14	19	0.01	28.0	27	0.01
KL34-05	482.6	485.7	0.61	6100	0.28	2.5	84	13	5	42	2	57	0.01	18.5	21	0.01
KL34-05	485.7	488.7	0.53	5300	0.26	1.3	76	13	2	11	1	37	0.01	9.5	29	0.01
KL34-05	488.7	491.7	1.76	17600	0.62	2.8	71	19	2	30	1	40	0.3	20.5	31	0.01
KL34-05	491.7	494.7	2.05	20500	0.92	4.2	91	22	3	7	2	47	0.5	12.0	27	0.01
KL34-05	494.7	497.7	1.54	15400	0.65	2.5	88	16	4	5	1	38	0.5	12.5	26	0.01
KL34-05	497.7	500.7	0.82	8200	0.41	1.4	64	17	3	26	0.01	29	0.01	9.8	23	0.01
KL34-05	500.7	503.7	0.86	8600	0.43	2.3	82	40	1	16	3	36	0.01	9.5	30	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL34-05	503.7	506.7	1.6	16000	0.8	2.1	134	12	1	8	0.01	38	0.2	15.5	23	0.01
KL34-05	506.7	509.7	0.73	7300	0.37	1.6	78	14	2	4	0.01	32	0.4	7.3	23	0.01
KL34-05	509.7	512.7	1.17	11700	0.66	1.8	111	11	2	3	0.01	44	0.01	9.5	29	0.01
KL34-05	512.7	515.7	0.9	9000	0.5	1.8	89	12	2	3	0.01	34	0.4	9.5	24	0.01
KL34-05	515.7	518.7	0.51	5100	0.25	1.1	42	16	15	63	0.01	14	0.6	11.3	28	0.01
KL34-05	518.7	521.7	0.64	6400	0.22	2.1	46	15	0.01	45	0.01	11	0.01	7.3	34	0.01
KL34-05	521.7	524.7	0.66	6600	0.21	2.6	55	17	5	24	1	16	0.2	16.8	95	0.01
KL34-05	524.7	527.7	0.84	8400	0.11	1.8	43	30	12	28	2	50	0.4	19.0	107	0.01
KL34-05	527.7	530.7	0.254	2540	0.04	0.9	29	12	4	175	0.01	9	0.01	6.3	131	0.01
KL34-05	530.7	533.7	0.281	2810	0.1	1.5	78	22	2	18	0.01	12	0.3	5.0	80	0.01
KL34-05	533.7	536.7	0.259	2590	0.09	1.1	43	8	2	57	0.01	9	0.3	6.5	72	0.01
KL34-05	536.7	539.3	0.425	4250	0.1	1.5	49	9	3	43	0.01	9	0.01	4.0	78	0.01
KL34-05	539.3	542.4	0.307	3070	0.11	1.2	50	11	3	117	0.01	11	0.4	6.3	65	0.01
KL34-05	542.4	545.4	0.267	2670	0.11	1.1	61	10	3	36	0.01	12	0.01	5.5	50	0.01
KL34-05	545.4	548.4	0.2	2000	0.18	0.7	42	9	2	18	0.01	10	0.2	5.0	39	0.01
KL34-05	548.4	551.5	0.255	2550	0.16	1.1	50	11	6	10	0.01	7	0.01	3.3	30	0.01
KL34-05	551.5	554.6	0.23	2300	0.12	1.2	92	15	3	19	0.01	10	0.2	3.0	39	0.01
KL34-05	554.6	557.7	0.359	3590	0.28	1	81	12	2	7	0.01	13	0.3	5.8	41	0.01
KL34-05	557.7	560.7	0.29	2900	0.09	1.6	50	8	5	28	0.01	7	0.2	3.8	72	0.01
KL34-05	560.7	563.7	0.27	2700	0.12	1.3	59	10	2	56	2	6	0.3	4.5	52	0.01
KL34-05	563.7	566.7	0.339	3390	0.21	1.4	91	7	2	21	0.01	10	0.4	3.8	46	0.01
KL34-05	566.7	569.7	0.19	1900	0.06	1.3	277	264	150	50	1	9	68	7.8	131	0.22
KL34-05	569.7	572.5	0.24	2400	0.06	1.7	265	125	370	25	1	10	112	9.5	133	0.38
KL34-05	572.5	574.7	0.3	3000	0.04	2.8	295	190	290	149	1	6	185	6.8	184	0.27
KL34-05	574.7	577	0.47	4700	0.14	1.9	52	15	6	92	0.01	35	0.01	9.8	110	0.01
KL34-05	577	579.9	0.18	1800	0.07	0.8	43	18	3	42	0.01	8	0.01	3.0	69	0.01
KL34-05	579.9	584.7	0.172	1720	0.05	1	112	58	15	74	1	5	0.6	3.5	169	0.01
KL34-05	584.7	587.7	0.24	2400	0.05	1.8	63	42	37	84	5	7	1.2	4.5	125	0.01
KL34-05	587.7	590.7	0.38	3800	0.12	2.2	65	28	21	109	2	11	1.7	6.8	224	0.11
KL34-05	590.7	593.7	0.45	4500	0.05	2.1	36	15	260	390	3	39	5.4	12.8	309	0.23
KL34-05	593.7	596.7	0.34	3400	0.1	1.9	43	27	29	518	1	12	1.1	6.5	207	0.01
KL34-05	596.7	599.7	0.28	2800	0.16	1.7	50	21	8	285	2	6	0.2	5.5	191	0.01
KL34-05	599.7	602.7	0.45	4500	0.17	2.8	150	41	150	192	2	13	4.6	5.0	196	0.18
KL34-05	602.7	605.7	0.46	4600	0.22	2.8	148	103	14	58	0.01	14	0.7	6.8	141	0.01
KL34-05	605.7	608.7	0.41	4100	0.06	2.4	408	217	3	71	0.01	7	0.01	3.8	118	0.01
KL34-05	608.7	611.7	0.39	3900	0.08	1.9	62	42	0.01	43	0.01	5	0.01	3.8	64	0.01
KL34-05	611.7	614.7	0.15	1500	0.05	0.8	26	13	2	20	0.01	2	0.01	1.3	13	0.01
KL34-05	614.7	616.9	0.32	3200	0.11	1.5	55	6	0.01	108	0.01	3	0.01	2.3	35	0.01
KL34-05	616.9	619.9	0.33	3300	0.04	1.6	160	47	2	51	1	6	0.01	3.3	54	0.01
KL34-05	619.9	623	0.52	5200	0.08	1.7	44	16	1	69	2	7	0.01	7.2	57	0.01
KL34-05	623	626.1	0.24	2400	0.07	0.9	71	43	1	40	0.01	7	0.01	2.3	22	0.01
KL34-05	626.1	629.2	0.26	2600	0.1	1	87	95	3	26	0.01	9	0.01	5.0	34	0.01
KL34-05	629.2	632.3	0.64	6400	0.3	1.8	72	13	2	18	0.01	41	0.01	13.4	48	0.01
KL34-05	632.3	635.4	0.66	6600	0.18	2.1	99	17	1	59	0.01	24	0.01	10.1	32	0.01
KL34-05	635.4	638.5	0.064	640	0.02	0.1	43	11	3	9	0.01	15	0.01	1.5	21	0.01
KL34-05	638.5	641.6	0.17	1700	0.05	0.1	27	6	1	7	0.01	12	0.01	3.5	26	0.01
KL34-05	641.6	644.6	0.097	970	0.02	0.1	60	10	3	115	0.01	17	0.01	3.8	57	0.01
KL34-05	644.6	647.7	0.146	1460	0.13	0.7	67	8	1	192	0.01	43	0.01	4.8	41	0.01
KL34-05	647.7	650.7	0.11	1100	0.03	0.1	57	9	2	5	0.01	18	0.01	1.3	43	0.01
KL34-05	650.7	653.7	0.2	2000	0.12	0.8	53	13	2	470	0.01	40	0.01	12.8	60	0.01
KL34-05	653.7	656.7	0.167	1670	0.05	0.7	47	11	3	42	0.01	13	0.01	3.0	32	0.01
KL34-05	656.7	659.7	0.61	6100	0.19	2.1	59	9	3	43	0.01	11	0.01	6.8	25	0.01
KL34-05	659.7	662.7	0.46	4600	0.21	1.5	111	60	2	135	0.01	16	0.01	6.5	44	0.01
KL34-05	662.7	665.7	0.125	1250	0.02	0.1	43	15	2	38	0.01	16	0.01	5.8	39	0.01
KL34-05	665.7	668.7	0.076	760	0.03	0.1	24	9	1	53	0.01	7	0.01	3.0	30	0.01
KL34-05	668.7	671.7	0.077	770	0.02	0.1	36	5	4	51	0.01	14	0.01	3.0	45	0.01
KL34-05	671.7	674.7	0.21	2100	0.04	0.6	32	5	6	45	0.01	19	0.01	7.3	41	0.01
KL34-05	674.7	677.7	0.54	5400	0.24	2.3	74	6	5	24	0.01	31	0.01	6.3	52	0.01
KL34-05	677.7	680.7	0.96	9600	0.58	4.8	98	6	4	29	0.01	36	0.01	8.3	60	0.01
KL34-05	680.7	683.7	0.26	2600	0.2	0.9	74	12	4	46	0.01	17	0.01	4.3	36	0.01
KL34-05	683.7	686.7	0.74	7400	0.35	1.8	130	7	1	550	0.01	33	2.6	8.0	26	0.01
KL34-05	686.7	689.7	0.24	2400	0.12	1	101	6	1	54	0.01	30	0.01	3.8	30	0.01
KL34-05	689.7	692.7	0.089	890	0.04	0.6	74	24	4	21	0.01	12	0.01	3.3	23	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL34-05	692.7	695.7	0.52		5200	0.26	1.4	101	6	1	27	0.01	32	3.8	5.1	28	0.01
KL34-05	695.7	698.7	0.38		3800	0.23	1	90	5	1	14	0.01	16	1.6	4.0	35	0.01
KL34-05	698.7	701.7	0.16		1600	0.06	0.1	49	7	2	16	0.01	18	0.9	4.3	41	0.01
KL34-05	701.7	704.7	0.075		750	0.02	0.1	33	6	0.01	13	0.01	11	0.2	1.3	21	0.01
KL34-05	704.7	707.7	0.12		1200	0.01	0.1	43	7	1	7	0.01	12	0.01	3.3	19	0.01
KL34-05	707.7	710.7	0.23		2300	0.18	0.8	61	6	1	21	0.01	18	0.2	4.5	24	0.01
KL34-05	710.7	713.9	0.057		570	0.06	0.6	54	6	1	8	0.01	11	0.01	0.0	31	0.01
KL34-05	713.9	716.7	0.05		500	0.01	0.1	71	26	4	51	0.01	15	0.2	7.5	25	0.01
KL34-05	716.7	719.7	0.2		2000	0.05	0.1	55	7	1	30	0.01	19	0.9	13.3	30	0.01
KL34-05	719.7	722.7	0.104		1040	0.01	0.1	46	10	2	35	0.01	18	0.01	4.8	25	0.01
KL34-05	722.7	725.7	0.185		1850	0.05	0.8	289	181	1	23	0.01	18	0.01	5.8	31	0.01
KL34-05	725.7	728.2	0.174		1740	0.09	0.8	36	9	0.01	33	0.01	18	0.01	9.7	22	0.01
KL34-05	728.2	731.2	0.071		710	0.01	0.1	10	5	0.01	11	0.01	3	0.01	2.5	30	0.01
KL34-05	731.2	734.2	0.078		780	0.02	0.1	12	6	0.01	12	0.01	2	0.01	1.0	46	0.01
KL34-05	734.2	737.3	0.155		1550	0.03	0.9	170	87	0.01	15	1	3	0.2	2.0	13	0.01
KL34-05	737.3	740.3	0.46		4600	0.2	1.1	129	42	0.01	76	0.01	16	0.01	7.1	22	0.01
KL34-05	740.3	743.3	0.08		800	0.02	0.1	27	7	0.01	148	0.01	9	0.01	1.8	10	0.01
KL34-05	743.3	746.4	0.145		1450	0.11	0.9	35	6	0.01	5	0.01	10	0.01	1.7	16	0.01
KL34-05	746.4	749.4	0.21		2100	0.09	1.1	30	8	1	303	0.01	9	0.2	7.5	12	0.01
KL34-05	749.4	752.5	0.183		1830	0.16	1	47	10	0.01	28	0.01	10	0.01	2.8	11	0.01
KL34-05	752.5	755.6	0.115		1150	0.06	0.9	41	7	0.01	17	0.01	11	0.01	2.3	8	0.01
KL34-05	755.6	758.7	0.168		1680	0.09	1.1	25	5	0.01	142	0.01	7	0.01	3.3	15	0.01
KL34-05	758.7	761.7	0.196		1960	0.09	1.1	141	113	0.01	186	0.01	9	0.01	6.3	9	0.01
KL34-05	761.7	764.7	0.081		810	0.02	0.9	25	10	0.01	15	0.01	5	0.01	1.0	8	0.01
KL34-05	764.7	767.7	0.074		740	0.14	0.1	18	6	0.01	18	0.01	5	0.01	1.5	9	0.01
KL34-05	767.7	770.7	0.09		900	0.15	0.9	18	7	2	6	1	6	0.2	2.0	9	0.01
KL34-05	770.7	773.7	0.78		7800	0.47	3.5	88	11	0.01	13	1	19	0.01	6.9	16	0.01
KL34-05	773.7	776.7	0.23		2300	0.27	1.1	40	5	0.01	11	1	8	0.01	3.0	12	0.01
KL34-05	776.7	779.7	0.12		1200	0.05	0.1	44	10	0.01	29	0.01	10	0.01	3.8	10	0.01
KL34-05	779.7	782.7	0.108		1080	0.07	0.1	41	5	0.01	15	0.01	8	0.01	2.3	10	0.01
KL34-05	782.7	785.7	0.083		830	0.06	1.1	27	5	0.01	11	0.01	7	0.3	1.9	9	0.01
KL34-05	785.7	788.7	0.158		1580	0.15	1.2	73	13	4	26	0.01	13	0.3	3.3	17	0.01
KL34-05	788.7	791.7	0.22		2200	0.27	1.4	59	8	1	9	1	12	0.3	4.8	27	0.01
KL34-05	791.7	794.7	0.44		4400	0.37	1.8	75	7	2	12	1	11	0.2	7.6	17	0.01
KL34-05	794.7	797.7	0.23		2300	0.28	2	103	6	1	4	1	19	0.01	6.0	20	0.01
KL34-05	797.7	800.7	0.195		1950	0.24	1.4	45	5	0.01	34	0.01	13	0.01	5.8	17	0.01
KL34-05	800.7	803.7	0.178		1780	0.23	1.5	29	5	1	26	1	10	0.01	5.4	8	0.01
KL34-05	803.7	806.7	0.058		580	0.02	0.1	13	7	0.01	10	0.01	4	0.01	1.8	6	0.01
KL34-05	806.7	809.5	0.06		600	0.01	0.7	16	12	0.01	30	0.01	3	0.01	1.8	8	0.01
KL34-06	0	2.8	0.0032		32	0.03	0.1	319	92	3	3	0.01	1	1.7	2.2	26	0.01
KL34-06	2.8	4.9	0.0018		18	0.03	0.1	410	127	8	5	0.01	1	1.8	2.0	37	0.01
KL34-06	4.9	8	0.0391		391	0.08	1.2	400	187	9	4	0.01	1	1.7	2.0	35	0.01
KL34-06	8	11.6	0.05		500	0.06	1	289	154	6	3	0.01	3	1.5	2.0	31	0.01
KL34-06	11.6	14.7	0.003		30	0.02	0.9	186	98	15	1	0.01	1	1.2	1.5	15	0.01
KL34-06	14.7	17.8	0.0029		29	0.02	1	254	104	11	1	0.01	1	0.8	2.0	20	0.01
KL34-06	17.8	20.8	0.0068		68	0.06	5	8500	1050	59	4	1	2	2.1	6.6	25	0.1
KL34-06	20.8	23.2	0.0051		51	0.05	2.5	4070	1020	23	1	0.01	2	2	5.2	20	0.1
KL34-06	23.2	26.3	0.0035		35	0.24	2.8	780	402	30	1	0.01	2	1	1.5	24	0.01
KL34-06	26.3	29.3	0.0062		62	0.22	5	3390	1740	20	1	0.01	1	2.8	1.8	20	0.28
KL34-06	29.3	32.3	0.0022		22	0.07	1.5	820	310	9	1	0.01	1	1.1	1.2	22	0.01
KL34-06	32.3	35.4	0.0325		325	0.03	1.5	127	93	4	1	0.01	1	0.7	1.0	21	0.01
KL34-06	35.4	38.4	0.108		1080	0.14	198	53700	45900	350	3	210	2	44	105.0	28	0.75
KL34-06	38.4	41.5	0.116		1160	0.1	44	23600	25800	270	12	41	4	78	230.0	63	0.97
KL34-06	41.5	44.6	0.0109		109	0.16	61	2100	28000	300	12	82	2	41	240.0	27	0.1
KL34-06	44.6	47.6	0.0032		32	0.06	1.1	450	229	7	3	0.01	1	1.9	5.1	25	0.14
KL34-06	47.6	50.8	0.0105		105	0.13	0.8	358	167	64	7	2	2	2	2.0	23	0.01
KL34-06	50.8	53.6	0.0047		47	0.03	0.6	151	74	4	1	0.01	3	0.9	2.5	21	0.01
KL34-06	53.6	56.8	0.0028		28	0.07	0.5	264	86	3	1	0.01	1	1.3	1.5	22	0.01
KL34-06	56.8	59.6	0.0095		95	0.2	0.6	1230	326	33	4	0.01	1	2.5	3.0	27	0.01
KL34-06	59.6	62.7	0.0116		116	0.01	0.1	276	88	9	3	0.01	1	0.6	2.2	34	0.01
KL34-06	62.7	65.8	0.0034		34	0.03	0.1	361	170	14	3	0.01	1	0.8	1.2	24	0.01
KL34-06	65.8	68.8	0.0039		39	0.02	0.1	126	46	57	2	0.01	1	1.9	2.0	40	0.01
KL34-06	68.8	71.8	0.0025		25	0.03	0.1	590	325	10	1	0.01	1	1.3	1.5	22	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL34-06	71.8	74.8	0.21	2100	0.19	3.5	1570	1180	130	7	4	8	5.2	5.8	62	0.01
KL34-06	74.8	77.6	0.0102	102	0.13	1.5	1260	530	35	41	2	3	4.7	3.0	33	0.1
KL34-06	77.6	80.2	0.0409	409	0.18	10.1	3990	2490	150	37	4	4	11.3	19.5	65	0.42
KL34-06	80.2	83.1	0.35	3500	0.45	302	29500	47000	800	16	44	2	72	103.0	54	3.48
KL34-06	83.1	86.8	0.0241	241	0.63	10	5400	5800	270	150	11	3	17.8	15.0	124	0.26
KL34-06	86.8	91.3	0.055	550	0.19	5.7	1530	840	61	16	18	5	6.9	23.5	85	0.01
KL34-06	91.3	93.7	0.0289	289	0.12	4.1	3700	500	61	12	47	9	5	11.8	103	0.01
KL34-06	93.7	96.8	0.079	790	0.16	16.5	4870	3150	270	11	66	5	26	11.2	94	0.24
KL34-06	96.8	100.2	0.042	420	0.15	13.3	9300	7900	97	14	33	3	20	16.5	155	0.2
KL34-06	100.2	103.1	0.0375	375	0.13	3	1370	392	110	15	8	2	20	3.8	187	0.1
KL34-06	103.1	107.3	0.0076	76	0.15	3.2	2660	900	48	11	2	1	3.5	3.0	90	0.1
KL34-06	107.3	110.8	0.083	830	0.29	4.4	2440	1720	82	16	4	1	5.3	6.2	76	0.13
KL34-06	110.8	113.8	0.198	1980	0.49	13.5	2450	1350	79	71	14	3	5.9	16.8	73	0.26
KL34-06	113.8	116.8	0.42	4200	0.44	20.8	6400	4200	450	243	130	17	20	23.5	38	0.1
KL34-06	116.8	119.8	0.415	4150	0.28	6.7	3070	1480	80	40	20	5	9.8	7.2	27	0.01
KL34-06	119.8	122.3	0.0151	151	0.3	2.8	1580	850	39	18	5	1	9.9	6.0	33	0.01
KL34-06	122.3	125.8	0.0176	176	0.18	3.6	2850	2270	29	27	6	1	7.2	8.0	20	0.01
KL34-06	125.8	128.8	0.0243	243	0.16	5.8	4130	1650	39	32	15	3	14.3	11.8	27	0.01
KL34-06	128.8	134.3	0.0203	203	0.28	3.8	2070	1170	49	57	6	2	12.4	9.5	18	0.01
KL34-06	134.3	137.3	0.0107	107	0.09	1.6	840	460	36	55	4	1	5.2	5.0	24	0.01
KL34-06	137.3	140.4	0.0088	88	0.09	3.3	2940	1170	22	129	7	1	5.3	6.5	23	0.01
KL34-06	140.4	143.5	0.01	100	0.08	2.9	900	590	30	44	3	1	4.4	5.2	25	0.01
KL34-06	143.5	146.3	0.0043	43	0.05	1.5	327	308	18	41	3	1	3.1	3.5	24	0.01
KL34-06	146.3	149.8	0.0108	108	0.08	3.6	2930	1460	28	128	9	1	6.2	6.8	23	0.01
KL34-06	149.8	152.8	0.0325	325	0.13	2.9	1150	490	31	69	8	1	3.4	7.0	20	0.01
KL34-06	152.8	156.1	0.052	520	0.1	8.8	3980	1710	38	119	26	1	6.9	16.0	13	0.01
KL34-06	156.1	160.2	0.0232	232	0.2	5.9	3260	2800	70	131	14	1	6.4	12.2	21	0.01
KL34-06	160.2	163.7	0.0145	145	0.07	2.2	1430	1310	21	66	4	1	2.1	5.0	16	0.01
KL34-06	163.7	167.2	0.013	130	0.1	3.7	2620	3200	20	38	6	1	4	9.7	16	0.01
KL34-06	167.2	170.8	0.0201	201	0.22	8.2	4370	3600	37	132	19	1	6	11.5	18	0.01
KL34-06	170.8	173.7	0.028	280	0.23	7.3	1990	1350	64	360	26	1	7	8.0	16	0.01
KL34-06	173.7	176.5	0.25	2500	0.52	23.8	10000	6600	760	1370	82	6	149	36.0	22	0.46
KL34-06	176.5	179.8	0.178	1780	0.31	28	8000	4700	670	925	64	4	42	14.5	23	0.27
KL34-06	179.8	182.8	0.106	1060	0.35	12.7	6600	4300	290	307	33	3	22	12.8	21	0.2
KL34-06	182.8	185.8	0.183	1830	0.27	19.4	18500	9500	400	120	32	4	46	22.4	20	0.21
KL34-06	185.8	188.8	0.174	1740	0.68	24.4	19400	15500	500	129	23	4	24	15.8	24	0.22
KL34-06	188.8	191.8	0.073	730	0.59	34	25700	27500	140	63	9	3	16	20.5	32	0.01
KL34-06	191.8	193.8	0.32	3200	1.99	37	30700	24900	130	90	49	6	9.6	98.0	38	0.01
KL34-06	193.8	197.8	0.75	7500	1.7	169	63000	18500	350	680	420	63	9.2	201.0	77	0.12
KL34-06	197.8	200.2	1.54	15400	2.27	116	67000	26600	250	12	310	8	6.3	125.0	91	0.34
KL34-06	200.2	203.8	1.89	18900	5.4	24.5	1550	630	200	15	260	38	5.2	64.8	132	0.28
KL34-06	203.8	206.4	1.11	11100	1.9	12.8	234	230	170	34	60	32	3.7	58.0	83	0.28
KL34-06	206.4	209.5	2.03	20300	1.89	26.3	400	176	200	274	80	71	4.9	36.0	67	0.24
KL34-06	209.5	212.6	0.41	4100	1.02	8.8	580	492	140	650	50	16	5.6	45.0	121	0.12
KL34-06	212.6	215.3	0.332	3320	0.65	7.7	720	298	140	500	36	14	6.9	27.0	126	0.12
KL34-06	215.3	218.8	1.9	19000	1.47	28.8	2500	490	210	181	50	51	10.1	36.0	114	0.32
KL34-06	218.8	221	1.92	19200	1.23	27.5	1500	720	150	314	40	30	5.7	35.0	115	0.46
KL34-06	221	224.1	0.67	6700	1.05	15.4	1580	610	58	117	19	25	4.8	22.0	138	0.3
KL34-06	224.1	227.7	1.78	17800	0.81	20	247	184	150	40	5	36	2.3	32.0	147	0.5
KL34-06	227.7	230.8	1.56	15600	0.68	6	119	146	100	111	4	52	3.4	66.5	115	0.1
KL34-06	230.8	233.8	2.55	25500	0.93	13.4	174	104	220	221	39	216	15.1	95.0	121	0.1
KL34-06	233.8	236.8	2.32	23200	0.84	10.3	87	71	100	352	5	62	1.9	55.0	112	0.18
KL34-06	236.8	239.8	3.98	39800	1.39	16	226	140	310	419	6	86	3.9	53.0	93	0.3
KL34-06	239.8	242.8	1.58	15800	0.72	4.7	181	133	160	134	5	104	1.8	43.0	128	0.1
KL34-06	242.8	245.2	1.39	13900	0.54	3	61	49	100	325	4	98	1.6	24.0	158	0.01
KL34-06	245.2	248.2	3.03	30300	1.42	16.8	540	204	350	418	8	134	6.5	26.0	98	0.32
KL34-06	248.2	251.3	3.01	30100	2.98	15.6	570	305	290	509	5	50	5.4	21.0	76	0.34
KL34-06	251.3	254.4	1.7	17000	1.25	8.4	138	78	350	345	7	81	30	23.5	120	0.12
KL34-06	254.4	257.7	3.33	33300	1.34	10.5	189	87	280	70	7	76	30.3	36.0	80	0.01
KL34-06	257.7	260.8	3.7	37000	3.03	14.4	1820	800	140	238	3	88	5.1	30.0	85	0.01
KL34-06	260.8	263.8	2.63	26300	3.06	12.5	1500	1440	120	77	3	112	5.3	25.0	72	0.01
KL34-06	263.8	266.5	3.35	33500	1.6	13.1	530	123	150	140	4	125	7.3	29.0	80	0.01
KL34-06	266.5	269.2	2.03	20300	1.16	8.6	171	106	180	123	5	49	9.4	24.0	125	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL34-06	269.2	272.2	1.49	14900	0.7	12.1	190	89	43	450	5	53	5.6	17.5	100	0.01
KL34-06	272.2	275.2	2.9	29000	1.1	30.6	110	68	1840	435	4	110	45	32.0	149	0.01
KL34-06	275.2	278.3	1.79	17900	1.06	19.2	700	128	460	133	5	67	12.2	28.0	98	0.1
KL34-06	278.3	281.5	1.95	19500	2.6	13.5	7200	2300	150	205	5	41	9.3	21.0	128	0.31
KL34-06	281.5	284.5	2.27	22700	1.8	11.1	325	154	170	313	3	64	13.9	28.5	117	0.16
KL34-06	284.5	287.4	1.43	14300	2.92	9.6	2100	640	140	207	6	42	6.7	24.0	125	0.01
KL34-06	287.4	290.3	1.51	15100	2.8	14.1	3400	2600	120	44	4	21	6.2	22.0	99	0.01
KL34-06	290.3	293.3	1.45	14500	2.16	10.8	342	262	150	50	5	36	3.5	28.5	90	0.01
KL34-06	293.3	296.8	2.8	28000	2.58	15.2	420	92	56	11	3	51	2.5	38.0	127	0.1
KL34-06	296.8	299.1	0.92	9200	4.99	10.1	1530	107	210	13	90	20	4.1	68.0	140	0.01
KL34-06	299.1	302.2	0.62	6200	6.2	7.4	430	286	150	76	140	19	2.9	95.0	95	0.01
KL34-06	302.2	305.3	0.35	3500	5.9	30	32000	22100	520	65	167	8	32	258.0	127	0.42
KL34-06	305.3	308.6	0.25	2500	4.4	60	61000	55800	550	119	86	13	79	262.0	98	0.9
KL34-06	308.6	311.7	0.25	2500	5.2	42	31300	23500	700	124	70	20	48	147.0	123	0.25
KL34-06	311.7	314.8	0.051	510	1.12	7.6	5300	2800	100	33	18	19	11.6	19.2	53	0.17
KL34-06	314.8	317.8	0.0269	269	1.01	6.6	3950	2000	180	30	19	4	7.2	9.2	50	0.01
KL34-06	317.8	320.8	0.048	480	1.14	10.2	10300	2000	120	59	61	3	9.2	17.0	51	0.22
KL34-06	320.8	323.8	0.0358	358	0.99	2.8	2870	700	160	33	18	8	9.3	11.2	55	0.01
KL34-06	323.8	326.8	0.058	580	0.53	2.2	1690	211	59	8	6	4	2.6	5.8	35	0.01
KL34-06	326.8	329.8	0.0174	174	0.36	3.3	1780	700	100	5	15	3	2.5	6.5	43	0.01
KL34-06	329.8	332.8	0.08	800	0.58	7.2	20000	1150	96	18	35	2	4.2	25.5	35	0.01
KL34-06	332.8	335.8	0.0151	151	0.44	1.1	870	295	130	13	9	4	4.9	4.2	46	0.01
KL34-06	335.8	338.8	0.0147	147	0.33	0.6	235	98	89	7	9	3	3.4	3.1	36	0.01
KL34-06	338.8	341.8	0.0136	136	0.62	0.5	376	132	72	6	8	2	2.3	4.3	34	0.01
KL34-06	341.8	344.8	0.049	490	0.12	0.9	410	267	34	5	1	4	2.9	3.2	36	0.01
KL34-06	344.8	347.8	0.0274	274	0.78	0.9	690	336	190	16	6	5	5.8	7.0	36	0.01
KL34-06	347.8	350.8	0.0208	208	0.97	1.2	540	200	160	21	34	5	5.8	9.4	31	0.19
KL34-06	350.8	353.8	0.043	430	0.45	0.6	252	40	110	10	4	6	3.6	2.2	31	0.01
KL34-06	353.8	356.8	0.0289	289	0.2	0.1	214	33	67	8	2	4	2.5	1.1	28	0.01
KL34-06	356.8	359.8	0.0168	168	0.08	0.1	170	34	40	3	1	3	1.5	0.7	18	0.01
KL34-06	359.8	362.8	0.0084	84	0.18	1.5	1000	353	31	2	1	1	2.9	2.3	22	0.1
KL34-06	362.8	365.8	0.0243	243	0.72	2.6	4300	4900	210	13	2	4	1.9	6.8	42	0.19
KL34-06	365.8	368.8	0.0087	87	0.17	0.1	186	84	130	8	1	2	2.4	0.8	21	0.01
KL34-06	368.8	371.8	0.0159	159	0.34	0.1	306	107	98	12	2	4	2.1	1.6	34	0.01
KL34-06	371.8	374.8	0.011	110	0.18	0.1	520	232	100	35	3	4	2.7	3.2	42	0.01
KL34-06	374.8	377.8	0.016	160	0.73	10.8	430	14500	87	39	4	3	10.4	368.0	50	0.01
KL34-06	377.8	380.8	0.0078	78	0.27	0.1	214	114	150	10	1	1	3.3	5.3	32	0.01
KL34-06	380.8	383.8	0.0084	84	0.27	1.6	1310	850	120	10	1	1	4.4	2.7	27	0.11
KL34-06	383.8	386.8	0.0086	86	0.44	0.1	470	192	140	8	1	2	4.1	2.9	39	0.01
KL34-06	386.8	389.8	0.047	470	1.31	19.3	4800	7800	430	26	6	1	30.8	7.4	48	0.31
KL34-06	389.8	392.8	0.067	670	0.27	1.4	195	355	100	520	6	9	2.5	2.5	121	0.01
KL34-06	392.8	395.8	0.0283	283	0.52	1	440	268	130	26	4	3	3.6	3.6	40	0.01
KL34-06	395.8	398.8	0.094	940	0.77	1.6	310	118	120	15	7	8	3.3	7.0	42	0.01
KL34-06	398.8	401.8	0.0305	305	0.98	0.8	220	118	100	10	5	3	3.1	3.6	41	0.01
KL34-06	401.8	404.8	0.0735	735	1.82	32.2	21100	20400	270	16	106	3	24	14.5	84	0.44
KL34-06	404.8	407.8	0.192	1920	1.02	2.9	5400	274	300	58	47	28	10.1	5.2	51	0.29
KL34-06	407.8	410.8	0.134	1340	0.49	6.6	4400	4400	160	82	34	10	10.6	24.0	33	0.1
KL34-06	410.8	413.8	0.058	580	0.67	7.6	12400	8500	240	10	8	3	13.5	20.5	32	0.16
KL34-06	413.8	416.8	0.07	700	1.72	15.7	28700	32100	420	31	34	4	28	224.0	67	0.26
KL34-06	416.8	419.8	0.73	7300	2.87	6.8	306	103	200	55	45	6	5.7	5.1	48	0.01
KL34-06	419.8	422.8	0.74	7400	2.93	5.1	480	282	360	143	120	7	12.3	5.7	49	0.01
KL34-06	422.8	426	2.08	20800	2.63	17.3	2100	1540	510	92	320	19	4.9	22.0	45	0.01
KL34-06	426	428.8	0.054	540	4.78	43	14800	35100	290	24	14	4	58	11.8	73	0.47
KL34-06	428.8	431.8	0.153	1530	0.24	3.3	383	490	66	348	8	3	3.1	3.4	67	0.01
KL34-06	431.8	434.8	0.149	1490	0.31	2.2	226	310	91	470	16	5	2.9	3.7	80	0.01
KL34-06	434.8	437.8	0.2505	2505	0.39	1.8	176	215	63	64	6	11	2.6	6.4	180	0.01
KL34-06	437.8	440.8	0.122	1220	0.3	9.1	288	1280	110	290	64	9	7.1	12.8	95	0.01
KL34-06	440.8	443.8	0.177	1770	0.29	3.3	339	450	79	158	22	8	2.4	6.2	164	0.01
KL34-06	443.8	446.8	0.089	890	0.38	10.4	3500	2900	160	430	69	22	5	18.5	187	0.01
KL34-06	446.8	449.8	0.132	1320	0.42	46	5600	41700	120	112	66	5	34	145.0	125	0.01
KL34-06	449.8	452.8	0.096	960	0.43	11.8	1720	11700	140	202	26	4	11.4	80.0	69	0.01
KL34-06	452.8	455.8	0.179	1790	0.36	5	1770	940	130	309	38	5	6.1	13.2	101	0.01
KL34-06	455.8	458.8	0.086	860	0.47	18.9	11800	33500	140	430	16	4	34	86.0	111	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL34-06	647.8	650.8															
KL34-06	650.8	653.8															
KL34-06	653.8	656.8															
KL34-06	656.8	659.8															
KL34-06	659.8	662.8															
KL34-06	662.8	665.8															
KL34-07	0	4.2	0.008		80	0.03	0.9	320	165	15	4	0.01	1	0.9	1.7	20	0.01
KL34-07	4.2	6.4	0.0033		33	0.08	2	820	306	26	9	1	1	2.5	4.2	33	0.1
KL34-07	6.4	9.7	0.0046		46	0.08	1.9	1760	344	25	5	0.01	1	2.1	2.7	23	0.1
KL34-07	9.7	14	0.0089		89	0.04	1.3	540	220	16	6	0.01	1	1.6	2.1	19	0.01
KL34-07	14	17.4	0.0059		59	0.03	1.6	750	400	18	7	1	1	1.5	3.2	13	0.01
KL34-07	17.4	20.4	0.0129		129	0.04	1.2	470	187	18	5	1	1	1.2	2.3	17	0.01
KL34-07	20.4	23.5	0.0087		87	0.02	1	275	136	20	4	2	3	0.5	2.0	23	0.01
KL34-07	23.5	26.7	0.0099		99	0.04	2.2	590	324	35	4	1	1	2.2	2.8	32	0.01
KL34-07	26.7	29.7	0.0061		61	0.16	1.5	325	158	24	3	1	2	1.2	1.7	27	0.01
KL34-07	29.7	32.7	0.0081		81	0.13	1.2	470	180	16	1	0.01	3	1.8	2.2	21	0.01
KL34-07	32.7	35.7	0.0044		44	0.1	0.5	158	90	14	2	0.01	1	0.5	1.4	19	0.01
KL34-07	35.7	37.4	0.0066		66	0.11	1	318	237	14	1	0.01	1	0.7	1.8	16	0.01
KL34-07	37.4	40.4	0.0047		47	0.08	0.8	242	100	10	1	0.01	1	1.2	1.4	20	0.01
KL34-07	40.4	44	0.0037		37	0.18	1	264	154	16	1	0.01	1	0.8	2.0	18	0.01
KL34-07	44	47.1	0.0234		234	0.19	8.3	1610	1700	48	7	16	4	4	13.8	27	0.14
KL34-07	47.1	49.5	0.107		1070	0.24	21.2	20100	14000	260	119	25	5	32	21.0	22	0.36
KL34-07	49.5	52.7	0.24		2400	0.38	345	70800	55300	420	6	830	10	44	560.0	28	0.5
KL34-07	52.7	56.4	0.065		650	0.16	11.6	6600	3480	60	36	41	6	49	52.0	41	0.17
KL34-07	56.4	59.5	0.0105		105	0.27	2.3	580	400	67	5	1	1	4.8	6.1	23	0.12
KL34-07	59.5	62.6	0.0399		399	0.08	1.5	490	301	34	19	4	2	1.5	5.2	23	0.1
KL34-07	62.6	65.7	0.0063		63	0.02	1	213	200	25	1	3	2	0.7	2.3	25	0.01
KL34-07	65.7	68.7	0.0085		85	0.02	2.1	790	381	27	1	3	3	1.3	3.2	24	0.01
KL34-07	68.7	71.7	0.007		70	0.04	0.6	142	80	14	1	0.01	1	0.7	1.5	20	0.01
KL34-07	71.7	74.7	0.015		150	0.07	0.6	319	120	17	3	1	2	1.4	1.7	23	0.01
KL34-07	74.7	77.7	0.0248		248	0.05	0.9	241	130	20	20	2	1	0.7	2.8	27	0.01
KL34-07	77.7	80.7	0.0133		133	0.06	1.1	284	241	34	3	1	2	1.3	2.3	27	0.1
KL34-07	80.7	83.7	0.007		70	0.23	4.7	890	570	100	4	1	3	6	8.1	26	0.16
KL34-07	83.7	86.7	0.0096		96	0.08	1.1	470	250	51	3	2	1	3	2.4	40	0.1
KL34-07	86.7	89.3	0.06		600	0.12	28	15000	13500	140	30	15	3	19.2	11.3	44	0.6
KL34-07	89.3	92.7	0.063		630	0.08	11.9	6700	4310	90	41	42	6	11.5	55.0	77	0.19
KL34-07	92.7	95.7	0.0134		134	0.22	11.4	2550	2710	61	12	6	4	11.3	14.5	21	0.47
KL34-07	95.7	98.3	0.061		610	0.36	13.4	2600	1500	240	9	73	4	47	120.0	104	0.2
KL34-07	98.3	101.7	0.0246		246	0.26	5.4	1680	620	100	6	20	1	32	6.7	125	0.1
KL34-07	101.7	105	0.0306		306	0.16	5.5	1810	510	170	5	33	3	30	5.8	118	0.13
KL34-07	105	108.1	0.0257		257	0.16	3.6	1270	410	110	14	12	2	12.3	7.0	131	0.1
KL34-07	108.1	110.6	0.0213		213	0.1	3.1	1520	560	56	8	4	1	7.3	3.9	146	0.1
KL34-07	110.6	113.7	0.048		480	0.09	5	1390	370	140	7	9	1	26	3.6	182	0.11
KL34-07	113.7	116.3	0.107		1070	0.12	3.5	2150	405	240	61	27	1	15.4	6.9	105	0.16
KL34-07	116.3	119.7	0.0167		167	0.17	3.1	2530	640	100	28	35	2	6.2	5.7	101	0.16
KL34-07	119.7	121.8	0.0097		97	0.15	3.8	5900	1200	94	7	21	5	8.2	7.1	100	0.13
KL34-07	121.8	124.8	0.0084		84	0.13	1.3	2680	440	84	17	2	2	4.5	3.9	102	0.1
KL34-07	124.8	127.8	0.0088		88	0.21	0.9	1520	227	120	90	5	3	5	2.7	75	0.01
KL34-07	127.8	131.8	0.0264		264	0.41	2.4	7200	530	240	433	16	4	11	11.6	104	0.22
KL34-07	131.8	134.8	0.073		730	0.6	7.2	12400	2000	300	368	30	6	30	19.2	100	0.37
KL34-07	134.8	137.3	0.0244		244	0.35	5	6500	2200	120	256	19	3	7	13.9	64	0.17
KL34-07	137.3	140.4	0.043		430	0.35	5.8	8300	1500	190	135	34	2	12.2	12.5	29	0.15
KL34-07	140.4	143.2	0.041		410	0.24	3.6	2980	970	120	62	12	7	11.8	6.5	21	0.01
KL34-07	143.2	146.2	0.0226		226	0.21	2.8	1900	670	93	37	8	2	4.7	6.8	23	0.01
KL34-07	146.2	149.2	0.0071		71	0.11	0.8	720	261	27	14	3	3	1.4	2.8	26	0.01
KL34-07	149.2	152.6	0.0085		85	0.14	0.6	510	160	27	10	1	1	1.3	1.4	22	0.01
KL34-07	152.6	155.7	0.0075		75	0.08	2.3	410	580	15	30	5	1	2	5.0	31	0.01
KL34-07	155.7	158.1	0.0136		136	0.09	1.9	1280	630	35	56	6	2	5.6	5.8	24	0.01
KL34-07	158.1	161.8	0.007		70	0.14	1.1	295	287	21	26	2	2	1.2	5.3	23	0.01
KL34-07	161.8	164	0.0076		76	0.08	1.5	500	353	13	75	4	2	1.6	3.8	26	0.01
KL34-07	164	166.1	0.0164		164	0.24	6.1	10000	1200	130	102	29	6	9	11.4	29	0.22
KL34-07	166.1	168.4	0.0156		156	0.12	2.3	640	392	33	210	6	2	2.6	6.0	24	0.01
KL34-07	168.4	171.2	0.127		1270	0.11	5.1	5900	840	120	87	17	13	9.5	8.0	18	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL34-07	171.2	173.7	0.0242	242	0.11	2.6	1420	560	48	265	9	5	4.1	6.8	23	0.01
KL34-07	173.7	176.7	0.0129	129	0.3	4.3	810	630	96	25	6	4	8.1	9.0	30	0.01
KL34-07	176.7	179	0.087	870	0.18	5.2	4800	1110	110	76	14	10	16	8.5	16	0.01
KL34-07	179	182.1	0.0132	132	0.18	3.3	1450	750	43	40	10	4	7.8	5.3	27	0.01
KL34-07	182.1	184.4	0.06	600	0.14	8.4	6300	2600	130	71	31	3	20	10.3	14	0.01
KL34-07	184.4	185.6	0.0254	254	0.15	4.6	3300	1100	62	55	18	7	7.9	10.5	17	0.01
KL34-07	185.6	188.5	0.037	370	0.14	5	4520	1070	96	55	28	7	7.1	11.5	14	0.01
KL34-07	188.5	191.3	0.28	2800	0.28	9.9	11200	2100	500	71	52	14	50	15.0	13	0.17
KL34-07	191.3	194.2	0.157	1570	0.22	8.2	8700	1690	310	82	40	7	42	14.3	16	0.14
KL34-07	194.2	197.7	0.126	1260	0.27	19.1	15800	8500	300	120	34	5	42	20.3	24	0.14
KL34-07	197.7	200.2	0.21	2100	0.35	35.3	32800	20000	340	126	42	6	64	31.0	26	0.17
KL34-07	200.2	203.2	0.22	2200	0.36	30.1	26500	17600	510	118	30	5	105	55.0	35	0.15
KL34-07	203.2	205.7	0.31	3100	0.45	37.4	37400	23300	530	162	38	8	102	38.2	31	0.27
KL34-07	205.7	208.8	0.056	560	0.35	26.7	12400	10000	120	32	30	2	28	18.2	30	0.1
KL34-07	208.8	211.1	0.51	5100	1.45	27.8	17800	4500	570	104	90	18	16.8	46.0	41	0.11
KL34-07	211.1	214.2	1.18	11800	2.5	21.5	3600	570	910	102	132	25	103	81.0	141	0.14
KL34-07	214.2	217.1	0.96	9600	1.04	12.7	289	231	1310	38	130	34	105	94.0	104	0.12
KL34-07	217.1	220	2.17	21700	2.36	15	150	120	440	112	94	54	48	67.0	105	0.19
KL34-07	220	223	6.47	64700	1.68	55	700	315	450	71	610	50	25.5	75.0	99	0.18
KL34-07	223	225.7	6.45	64500	1.22	53	289	86	1890	43	680	99	102	80.0	47	0.34
KL34-07	225.7	227.6	1.59	15900	0.86	17	140	126	1390	195	78	60	86	54.0	91	0.1
KL34-07	227.6	230	1.16	11600	0.54	8.5	107	104	170	870	30	37	5.8	40.5	133	0.12
KL34-07	230	233.1	2.2	22000	0.76	14.6	620	375	360	1720	28	25	35	41.0	114	0.2
KL34-07	233.1	235.9	1.06	10600	0.76	10	110	90	400	510	12	54	24.3	46.8	63	0.01
KL34-07	235.9	237.3	0.8	8000	0.74	10.3	2500	1660	990	800	18	19	45	36.0	103	0.14
KL34-07	237.3	239.7	3.54	35400	0.8	17.6	1480	590	330	740	42	66	3.2	41.5	103	0.24
KL34-07	239.7	242	5.1	51000	1.5	42	670	107	160	168	198	159	6.2	80.0	120	0.14
KL34-07	242	244.8	3.32	33200	1.76	33.4	1090	320	190	225	70	130	10.4	39.0	98	0.18
KL34-07	244.8	247.4	2.08	20800	1.5	16.7	2100	2800	180	22	46	120	6.8	67.0	122	0.01
KL34-07	247.4	250.5	1.75	17500	1.72	12.1	600	1290	100	30	74	20	5.9	71.0	100	0.01
KL34-07	250.5	252.5	1.45	14500	4.2	19.2	6800	3300	300	275	186	47	13.9	70.0	108	0.01
KL34-07	252.5	254.5	1.84	18400	2.25	46	25600	8100	3200	323	188	16	110	65.0	73	0.54
KL34-07	254.5	256.7	0.0202	202	0.14	4.8	1690	1000	47	54	5	1	5.6	20.0	24	0.17
KL34-07	256.7	259.8	1.33	13300	1.12	137	63400	68400	410	1220	660	50	42	4500.0	66	0.12
KL34-07	259.8	262.9	0.27	2700	0.73	25.6	10000	8900	120	225	51	13	15.3	132.0	67	0.16
KL34-07	262.9	265.4	0.27	2700	1	37.3	15600	13200	260	337	36	11	26	50.0	82	0.48
KL34-07	265.4	268.4	0.184	1840	0.36	13.6	8500	9400	280	117	23	4	22	32.0	31	0.18
KL34-07	268.4	271.2	0.0127	127	0.04	2.7	470	287	29	36	3	1	1.4	2.2	20	0.1
KL34-07	271.2	272.9	0.0085	85	0.15	2.6	408	283	53	18	0.01	1	2	3.0	27	0.11
KL34-07	272.9	276.6	0.0195	195	0.22	8	1430	930	73	21	2	1	6.6	7.2	30	0.16
KL34-07	276.6	280.1	0.016	160	0.1	1.5	940	530	29	12	1	1	1.2	4.9	20	0.01
KL34-07	280.1	282.5	0.0094	94	0.04	0.6	220	95	24	31	1	1	0.7	1.7	18	0.01
KL34-07	282.5	284.7	0.0123	123	0.05	0.8	1380	197	26	21	1	1	0.5	2.9	17	0.01
KL34-07	284.7	287.4	0.0079	79	0.03	0.5	440	120	19	10	0.01	1	0.4	1.5	15	0.01
KL34-07	287.4	290.2	0.0103	103	0.02	0.1	210	81	19	23	0.01	1	0.6	0.8	15	0.01
KL34-07	290.2	293	0.0126	126	0.02	0.7	297	122	33	17	0.01	1	1.1	2.4	16	0.01
KL34-07	293	296.2	0.0129	129	0.05	0.7	295	200	26	20	0.01	1	0.9	1.0	18	0.01
KL34-07	296.2	299.8	0.01	100	0.03	0.5	250	116	22	28	0.01	1	1	1.3	15	0.01
KL34-07	299.8	302.2	0.012	120	0.18	1.3	1380	530	41	21	0.01	1	1.5	3.2	15	0.01
KL34-07	302.2	305.7	0.0227	227	0.04	2.6	190	470	22	26	6	2	0.8	3.4	15	0.01
KL34-07	305.7	308.3	0.0109	109	0.11	0.6	356	171	34	70	0.01	1	1.3	1.7	16	0.01
KL34-07	308.3	310.7	0.0121	121	0.08	0.6	243	312	24	15	1	1	0.9	0.9	14	0.01
KL34-07	310.7	312.4	0.0105	105	0.37	1.7	189	800	31	47	2	1	2.6	4.0	17	0.01
KL34-07	312.4	316.3	0.0132	132	0.23	1.6	243	1140	34	20	3	1	3.1	4.4	21	0.01
KL34-07	316.3	319.4	0.0171	171	0.29	1.3	301	293	79	47	5	1	7.1	6.1	22	0.13
KL34-07	319.4	322.5	0.0335	335	0.28	2	2990	1000	82	28	5	2	12.7	5.4	25	0.18
KL34-07	322.5	324.5	0.0163	163	0.15	7.4	2870	1780	63	36	28	1	3.4	8.5	17	0.1
KL34-07	324.5	326.7	0.049	490	0.02	0.1	200	35	23	480	0.01	1	0.6	1.3	15	0.01
KL34-07	326.7	329.7	0.0227	227	0.04	2.6	190	470	22	26	6	2	0.8	3.4	15	0.01
KL34-07	329.7	332.7	0.048	480	0.42	5.2	2200	1740	150	106	19	10	10.4	31.0	51	0.12
KL34-07	332.7	335.7	0.23	2300	0.14	7.6	860	690	58	37	23	2	3.3	6.1	21	0.01
KL34-07	335.7	338.7	0.13	1300	0.1	4.2	510	249	50	40	6	3	3.2	5.4	17	0.01
KL34-07	338.7	341.7	0.032	320	0.07	0.6	129	65	37	7	2	1	1.7	3.6	16	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL34-07	341.7	344.7	0.0221		221	0.09	1.1	302	211	38	26	3	1	2.6	4.8	14	0.01
KL34-07	344.7	347.7	0.045		450	0.08	1.7	630	272	49	23	4	1	1.8	4.1	13	0.01
KL34-07	347.7	350.2	0.0118		118	0.09	0.9	196	215	38	16	2	1	1.7	3.3	17	0.01
KL34-07	350.2	353.2	0.0344		344	0.15	2.6	870	1040	54	38	6	1	4.6	8.4	16	0.11
KL34-07	353.2	356.3	0.052		520	0.21	3.7	780	1100	48	36	7	3	6.2	12.1	17	0.1
KL34-07	356.3	359.4	0.0178		178	0.09	2.2	630	1300	33	31	4	1	3.9	12.4	15	0.01
KL34-07	359.4	362.4	0.0175		175	0.05	0.6	420	179	41	23	3	1	1.5	2.8	14	0.01
KL34-07	362.4	365.4	0.02		200	0.07	0.8	530	214	37	42	3	1	2.1	3.6	16	0.01
KL34-07	365.4	368.4	0.0219		219	0.15	1.1	331	490	52	36	3	1	3.3	5.8	17	0.11
KL34-07	368.4	371.5	0.0285		285	0.26	2	480	960	61	45	4	1	5.7	5.8	24	0.18
KL34-07	371.5	374.5	0.041		410	0.13	1	104	80	41	45	6	1	4.5	4.3	17	0.1
KL34-07	374.5	377.6	0.0136		136	0.1	0.7	162	282	37	25	2	1	2.4	2.9	19	0.1
KL34-07	377.6	380.7	0.0277		277	0.15	1.9	620	630	43	36	5	1	3.3	8.4	15	0.1
KL34-07	380.7	383.7	0.0215		215	0.08	0.1	55	36	44	13	1	1	1.8	1.1	16	0.01
KL34-07	383.7	386.7	0.013		130	0.12	0.1	130	94	57	33	2	1	2.7	2.8	21	0.13
KL34-07	386.7	389.7	0.0281		281	0.11	0.1	103	64	64	36	2	1	3.2	1.5	18	0.11
KL34-07	389.7	392.7	0.0115		115	0.08	1.2	870	361	51	9	2	1	1.6	3.5	17	0.22
KL34-07	392.7	395.7	0.0143		143	0.1	0.1	156	84	56	10	2	1	2.3	3.4	18	0.11
KL34-07	395.7	398.7	0.0145		145	0.26	2.3	1970	820	76	18	4	1	7.4	4.8	17	0.3
KL34-07	398.7	401.7	0.0088		88	0.07	0.1	197	45	57	7	0.01	1	1.4	15	0.01	
KL34-07	401.7	404.7	0.0271		271	0.05	0.1	130	145	41	31	1	1	3.8	14	0.1	
KL34-07	404.7	407	0.017		170	0.07	0.1	157	146	46	33	1	1	0.9	3.9	15	0.11
KL34-07	407	410.7	0.0139		139	0.05	0.1	268	46	45	14	1	1	1.3	0.9	19	0.01
KL34-07	410.7	413	0.047		470	0.13	1.6	1750	1110	42	16	2	1	1.7	16.0	22	0.01
KL34-07	413	415.3	0.56		5600	1.44	6.3	3960	216	230	440	24	12	2	3.5	32	0.01
KL34-07	415.3	417.4	8.74		87400	10	57	15700	148	2120	652	630	129	6.8	32.5	33	0.01
KL34-07	417.4	419.7	0.27		2700	0.34	4	490	20	120	14	20	2	0.5	1.2	17	0.1
KL34-07	419.7	422.7	0.25		2500	0.29	3.2	430	21	130	131	16	3	0.7	1.3	18	0.01
KL34-07	422.7	425.7	0.045		450	0.16	1.6	1660	1080	80	30	2	1	2.6	20.8	24	0.01
KL34-07	425.7	428.7	0.0218		218	0.08	0.1	235	114	36	12	1	1	0.9	3.5	18	0.01
KL34-07	428.7	431.7	0.069		690	0.1	4.4	7400	2900	35	56	3	1	4	12.5	15	0.01
KL34-07	431.7	434.1	0.0291		291	0.11	3.3	730	1030	47	36	6	1	5.1	8.2	15	0.01
KL34-07	434.1	437.1	0.138		1380	0.22	9.4	11800	5700	45	45	6	3	10.1	16.2	15	0.1
KL34-07	437.1	439.1	0.078		780	0.27	1.3	870	346	30	79	1	1	1.8	3.3	14	0.01
KL34-07	439.1	440.7	0.0165		165	0.05	4.5	2150	1890	25	24	0.01	1	6.3	4.0	14	0.01
KL34-07	440.7	443.7	0.052		520	0.02	1	480	265	21	5	0.01	2	2.7	1.3	13	0.01
KL34-07	443.7	446.7	0.077		770	0.25	1.2	245	124	32	145	1	3	1.9	2.2	14	0.01
KL34-07	446.7	449.7	0.064		640	0.03	3.7	3030	1740	19	8	0.01	1	5.7	3.0	12	0.01
KL34-07	449.7	452.7	0.0075		75	0.06	0.1	55	28	48	7	1	1	1.3	1.3	17	0.01
KL34-07	452.7	455.7	0.006		60	0.02	0.1	39	39	27	4	0.01	1	0.2	1.4	18	0.01
KL34-07	455.7	458.7	0.0347		347	0.02	0.1	64	26	23	335	0.01	1	0.4	0.8	15	0.01
KL34-07	458.7	461.7	0.019		190	0.08	0.1	36	19	35	214	0.01	1	0.9	1.5	15	0.01
KL34-07	461.7	464.7	0.0072		72	0.05	0.1	46	16	53	21	0.01	1	0.8	0.7	17	0.01
KL34-07	464.7	467.7	0.073		730	0.12	0.7	490	25	85	71	1	3	3.5	1.6	16	0.13
KL34-07	467.7	470.7	0.0313		313	0.08	0.1	200	85	85	26	2	2	1.7	1.7	22	0.01
KL34-07	470.7	473.7	0.0237		237	0.06	0.1	205	69	81	25	2	3	1.6	1.0	21	0.01
KL34-07	473.7	476.7	0.0244		244	0.08	2.3	650	1360	35	34	4	3	3.4	10.3	15	0.01
KL34-07	476.7	479.7	0.042		420	0.03	0.1	270	37	73	27	1	1	1.3	1.2	25	0.01
KL34-07	479.7	482.7	0.0143		143	0.05	0.1	91	20	55	31	1	1	0.9	0.6	26	0.01
KL34-07	482.7	485.7	0.1		1000	0.33	1.4	740	34	250	65	0.01	3	2.9	2.0	25	0.13
KL34-07	485.7	488.7	0.0226		226	0.26	0.1	72	25	180	45	0.01	2	2.2	1.1	22	0.01
KL34-07	488.7	491.7	0.12		1200	0.04	0.8	224	54	43	145	3	3	1.1	2.7	24	0.01
KL34-07	491.7	494	0.0156		156	0.02	0.1	85	77	26	20	0.01	1	0.6	0.8	14	0.01
KL34-07	494	497.5	0.0259		259	0.01	0.1	65	19	15	34	0.01	1	0.01	0.6	18	0.01
KL34-07	497.5	500.3	0.0091		91	0.02	0.1	79	70	14	4	0.01	1	0.01	0.5	24	0.01
KL34-07	500.3	503.3	0.0054		54	0.01	0.1	26	16	12	1	0.01	1	0.01	0.0	20	0.01
KL34-07	503.3	506.4	0.008		80	0.01	0.1	43	28	15	11	0.01	1	0.2	1.1	14	0.01
KL34-07	506.4	509.5	0.0311		311	0.02	0.1	236	40	61	24	3	1	0.9	0.9	22	0.01
KL34-07	509.5	512.6	0.016		160	0.01	0.1	313	49	41	12	4	1	0.5	1.3	14	0.01
KL34-07	512.6	515.7	0.0127		127	0.02	0.1	540	30	24	4	0.01	1	0.2	0.0	10	0.01
KL34-07	515.7	518.7	0.0087		87	0.01	0.1	68	23	19	3	0.01	1	0.2	0.7	10	0.01
KL34-08	0	3	0.0267		267	0.01	0.7	206	98	12	5	0.01	1	1.2	1.0	46	0.01
KL34-08	3	6	0.0232		232	0.01	1.4	369	191	21	7	0.01	1	1	1.2	46	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL34-08	6	9	0.009		90	0.01	0.5	195	72	12	4	0.01	1	0.8	0.6	40	0.01
KL34-08	9	11.4	0.017		170	0.01	0.6	177	76	11	5	0.01	1	0.9	0.9	27	0.01
KL34-08	11.4	14.5	0.0053		53	0.01	0.8	283	85	14	5	0.01	1	0.8	1.0	24	0.01
KL34-08	14.5	17.6	0.0102		102	0.01	1	208	80	11	12	1	1	2.4	1.0	46	0.01
KL34-08	17.6	20.7	0.0124		124	0.01	0.1	150	46	11	6	0.01	1	1.1	0.7	21	0.01
KL34-08	20.7	23.8	0.0048		48	0.01	0.7	61	30	5	7	0.01	1	0.01	0.8	31	0.01
KL34-08	23.8	26.8	0.0094		94	0.02	0.5	148	57	11	18	0.01	1	1.4	1.0	17	0.01
KL34-08	26.8	29.8	0.0148		148	0.03	0.6	174	94	15	23	1	2	0.7	1.7	22	0.01
KL34-08	29.8	32.8	0.0047		47	0.01	0.7	200	68	11	7	0.01	1	0.6	1.0	29	0.01
KL34-08	32.8	35.8	0.0038		38	0.01	0.5	204	63	16	6	1	1	0.7	0.8	23	0.01
KL34-08	35.8	38.8	0.0126		126	0.01	1.9	321	367	40	10	0.01	3	2	1.7	31	0.01
KL34-08	38.8	41.8	0.02		200	0.04	4.3	5540	1940	48	3	0.01	1	3.4	2.2	26	0.72
KL34-08	41.8	44.8	0.0031		31	0.01	1.3	510	190	19	6	0.01	1	0.7	0.8	27	0.01
KL34-08	44.8	47.8	0.0058		58	0.13	3.2	3820	2420	20	4	0.01	1	1	3.0	28	0.21
KL34-08	47.8	50.8	0.0093		93	0.17	7.2	7300	6300	24	5	0.01	1	12.3	7.3	27	0.27
KL34-08	50.8	53.8	0.0093		93	0.13	3.1	4330	4140	20	5	0.01	1	4.8	1.7	27	0.22
KL34-08	53.8	56.8	0.003		30	0.11	0.7	1160	900	22	6	0.01	1	4	1.5	24	0.14
KL34-08	56.8	59.8	0.0049		49	0.53	2.1	8000	3500	37	6	0.01	1	19	3.9	28	0.46
KL34-08	59.8	62.8	0.002		20	0.06	0.6	251	160	7	6	0.01	1	0.6	1.5	14	0.01
KL34-08	62.8	65.8	0.0017		17	0.02	0.8	530	298	7	3	0.01	1	1	1.0	15	0.01
KL34-08	65.8	68.8	0.0013		13	0.01	1.9	670	830	29	6	0.01	7	1.1	3.5	26	0.01
KL34-08	68.8	71.8	0.0019		19	0.01	0.8	420	378	32	5	0.01	2	0.7	1.2	28	0.1
KL34-08	71.8	74.8	0.0059		59	0.02	2.2	1300	780	26	11	2	2	3.3	4.7	28	0.01
KL34-08	74.8	77.8	0.0149		149	0.01	3.3	3590	2130	28	4	1	1	4.5	2.7	28	0.1
KL34-08	77.8	80.8	0.0023		23	0.01	2.3	354	1670	28	5	0.01	3	2	1.5	27	0.01
KL34-08	80.8	83.8	0.0009		9	0.01	1	127	334	24	9	0.01	2	0.7	1.1	24	0.01
KL34-08	83.8	86.8	0.0029		29	0.02	0.9	305	620	23	6	0.01	1	0.7	1.7	21	0.01
KL34-08	86.8	89.8	0.004		40	0.01	3.3	640	1040	33	138	10	1	1.2	6.5	26	0.01
KL34-08	89.8	92.8	0.0033		33	0.01	2.3	103	167	18	50	19	1	0.8	4.2	21	0.01
KL34-08	92.8	95.8	0.0027		27	0.01	0.9	77	136	16	18	2	1	0.3	1.0	19	0.01
KL34-08	95.8	98.8	0.0052		52	0.01	2.9	730	2920	29	23	2	1	3.1	15.0	35	0.01
KL34-08	98.8	101.8	0.0034		34	0.02	1.6	280	740	43	62	2	1	1	3.8	33	0.01
KL34-08	101.8	104.8	0.0042		42	0.02	2.6	940	1390	100	5	4	3	1.5	4.7	41	0.1
KL34-08	104.8	107.2	0.0039		39	0.01	1	263	362	31	5	0.01	1	1	3.0	27	0.01
KL34-08	107.2	110.5	0.0025		25	0.01	0.8	154	236	13	7	1	1	0.7	3.2	19	0.01
KL34-08	110.5	113.7	0.0058		58	0.01	3.7	520	336	10	18	28	1	0.7	10.2	18	0.01
KL34-08	113.7	116.8	0.0039		39	0.01	1.6	294	289	19	5	7	1	0.7	2.5	27	0.01
KL34-08	116.8	119.8	0.0022		22	0.02	1.5	123	109	37	27	17	1	1	4.7	32	0.01
KL34-08	119.8	122.8	0.0037		37	0.01	1.9	328	450	21	9	2	1	0.7	2.0	16	0.01
KL34-08	122.8	125.8	0.0041		41	0.01	1.8	880	377	20	15	5	1	0.6	3.0	21	0.01
KL34-08	125.8	128.8	0.0094		94	0.01	1	231	93	15	3	4	1	0.5	2.5	32	0.01
KL34-08	128.8	131.8	0.0068		68	0.01	1.2	216	128	31	52	8	1	0.8	3.7	48	0.01
KL34-08	131.8	134.8	0.019		190	0.01	1.5	520	260	41	21	7	2	1.4	4.0	45	0.01
KL34-08	134.8	137.8	0.118		1180	0.02	2.3	227	224	77	73	9	29	3.1	13.2	67	0.01
KL34-08	137.8	140.8	0.0204		204	0.02	1.7	257	396	33	218	4	6	5.6	4.4	115	0.01
KL34-08	140.8	143.8	0.0312		312	0.01	1.5	183	460	42	90	2	3	2.3	1.8	142	0.01
KL34-08	143.8	146.8	0.0283		283	0.02	1.5	144	251	31	81	3	2	2.2	2.2	164	0.01
KL34-08	146.8	148.6	0.48		4800	0.15	7.3	124	630	29	352	32	14	3.8	17.2	156	0.01
KL34-08	148.6	152.5	0.055		550	0.21	7	510	1340	58	281	56	2	16.5	63.3	136	0.01
KL34-08	152.5	155.8	0.134		1340	0.03	3.9	121	266	21	44	9	1	4.8	4.6	73	0.01
KL34-08	155.8	158.8	0.3		3000	0.16	15.8	720	610	110	73	92	4	17.5	7.3	100	0.01
KL34-08	158.8	161.8	0.22		2200	0.09	3.6	265	124	98	133	19	1	11.8	6.0	229	0.01
KL34-08	161.8	164.8	0.54		5400	0.34	7.2	308	186	80	87	22	6	11.3	11.7	213	0.1
KL34-08	164.8	167.6	0.504		5040	0.24	6.6	165	144	68	70	26	6	3.7	11.0	161	0.01
KL34-08	167.6	170.7	0.26		2600	0.1	4.7	76	116	25	76	6	5	1.3	5.0	135	0.01
KL34-08	170.7	173.8	0.127		1270	0.07	5.2	74	338	48	35	18	4	1.4	2.7	124	0.01
KL34-08	173.8	176.8	0.167		1670	0.1	4.2	173	306	44	75	21	4	2.6	4.1	141	0.01
KL34-08	176.8	179.8	0.372		3720	0.16	8.6	174	440	100	118	85	13	3.6	12.2	90	0.01
KL34-08	179.8	182.8	0.082		820	0.06	2.4	102	89	23	310	20	3	2.3	8.5	47	0.01
KL34-08	182.8	185.8	0.128		1280	0.12	2	117	118	58	541	10	4	3.1	7.0	15	0.01
KL34-08	185.8	188.8	0.118		1180	0.18	5.1	1050	480	93	265	62	7	4.3	26.3	96	0.01
KL34-08	188.8	191.8	0.31		3100	0.68	29.1	30000	10900	210	1540	241	6	8.5	93.3	101	0.1
KL34-08	191.8	194.8	0.29		2900	0.16	6.1	9200	1100	200	128	52	4	3.7	15.0	56	0.1

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL34-08	194.8	197.8	0.15	1500	0.09	3.2	4190	500	310	25	5	2	7.9	6.0	30	0.13
KL34-08	197.8	200.1	0.063	630	0.07	5.3	8100	1560	200	31	18	1	8.4	13.0	26	0.15
KL34-08	200.1	203.1	0.04	400	0.04	5.7	14700	560	17	53	17	1	1.9	10.0	24	0.22
KL34-08	203.1	206.8	0.0395	395	0.12	5.6	29900	580	110	59	19	1	5.9	9.5	48	0.1
KL34-08	206.8	211.2	0.482	4820	0.18	6	4850	197	240	20	10	3	4.7	12.2	49	0.1
KL34-08	211.2	214.9	0.54	5400	0.21	7.5	5800	670	430	16	8	6	23	14.0	52	0.01
KL34-08	214.9	218.2	0.124	1240	0.09	3.3	24900	760	130	15	6	3	13.9	7.0	38	0.12
KL34-08	218.2	221.8	0.66	6600	0.19	7.8	23300	1050	320	21	32	11	25	11.5	65	0.12
KL34-08	221.8	225	0.064	640	0.03	1.8	4650	1050	100	14	4	1	8.8	6.2	30	0.01
KL34-08	225	227.8	0.25	2500	0.17	12	14100	2900	150	33	22	6	11.6	17.0	54	0.01
KL34-08	227.8	231.1	0.56	5600	0.22	18.9	10100	4500	640	40	10	9	16.7	23.8	58	0.16
KL34-08	231.1	235	0.12	1200	0.14	33.9	43600	8100	41	58	141	1	6.4	93.8	29	0.01
KL34-08	235	238.1	0.0218	218	0.05	4.1	3600	2480	29	15	6	1	2.9	16.0	20	0.01
KL34-08	238.1	240.6	0.0206	206	0.08	9	4800	2790	30	34	20	1	1.4	40.9	12	0.01
KL34-08	240.6	244	0.0125	125	0.03	2	1640	690	13	14	7	1	0.2	4.5	16	0.01
KL34-08	244	248.3	0.0342	342	0.06	1.8	1450	520	34	9	4	2	1.5	6.0	21	0.01
KL34-08	248.3	250.9	0.085	850	0.04	8.7	12800	9500	52	10	7	7	6.6	31.5	13	0.01
KL34-08	250.9	254.5	0.0182	182	0.04	1.8	650	313	24	10	4	1	1.5	3.2	15	0.01
KL34-08	254.5	258.3	0.0341	341	0.15	8.7	10900	3100	25	12	50	1	6.3	20.5	19	0.1
KL34-08	258.3	262.1	0.0094	94	0.02	3	980	450	12	20	9	1	1	4.2	16	0.01
KL34-08	262.1	266.3	0.0212	212	0.11	6.3	5940	2480	36	9	50	1	4.2	15.0	16	0.01
KL34-08	266.3	268.8	0.0403	403	0.06	5	1920	1210	64	21	850	1	8.9	12.8	19	0.01
KL34-08	268.8	271.8	0.0296	296	0.04	2	1010	480	51	14	324	2	2.1	6.7	16	0.01
KL34-08	271.8	273.9	0.014	140	0.02	0.9	2950	375	12	9	3	1	1	3.5	14	0.01
KL34-08	273.9	277.1	0.0071	71	0.01	0.1	1230	202	11	12	4	1	1	2.0	15	0.01
KL34-08	277.1	280.2	0.0326	326	0.07	0.9	1350	680	38	10	6	1	2.5	4.0	11	0.01
KL34-08	280.2	283.3	0.0165	165	0.05	1.3	830	500	36	46	143	2	1.6	5.0	16	0.01
KL34-08	283.3	286.3	0.0164	164	0.04	1.6	640	334	31	17	9	1	1.5	2.7	17	0.01
KL34-08	286.3	289.4	0.0112	112	0.02	2.6	830	520	24	16	20	1	1.5	4.2	14	0.01
KL34-08	289.4	292.2	0.0117	117	0.04	1.6	960	550	17	26	48	1	1.1	3.0	16	0.01
KL34-08	292.2	296.2	0.0135	135	0.05	7.9	1950	990	15	16	32	1	0.6	5.5	13	0.01
KL34-08	296.2	299.8	0.0285	285	0.15	3	1790	540	61	25	5	2	1.7	9.3	18	0.01
KL34-08	299.8	301.8	0.045	450	0.11	5.7	7100	6300	33	8	5	2	12	12.0	20	0.01
KL34-08	301.8	304.8	0.412	4120	0.22	4.1	2480	530	100	10	10	8	4.1	6.0	23	0.01
KL34-08	304.8	307.8	0.26	2600	0.19	4.9	1030	480	55	12	5	6	3.4	6.8	19	0.01
KL34-08	307.8	310.8	0.163	1630	0.6	5	6500	302	37	332	37	21	3.4	8.1	38	0.01
KL34-08	310.8	313.8	0.023	230	0.29	1.2	219	73	36	1310	8	4	0.7	2.3	25	0.01
KL34-08	313.8	316.8	0.0148	148	0.12	2.6	155	232	21	287	8	3	1	3.0	28	0.01
KL34-08	316.8	319.8	0.59	5900	0.72	3.8	296	207	69	191	11	26	4	9.8	57	0.01
KL34-08	319.8	322.8	1.4	14000	0.91	13.8	1310	384	38	85	5	86	3.6	13.5	50	0.01
KL34-08	322.8	325.8	1.15	11500	1	16.9	2090	720	58	104	76	60	6.6	11.5	42	0.01
KL34-08	325.8	328.8	0.94	9400	0.78	19	7900	560	75	401	38	89	3.1	13.0	21	0.01
KL34-08	328.8	331.8	1.31	13100	1.02	35.8	12000	1010	34	320	91	48	0.6	15.5	33	0.01
KL34-08	331.8	334.8	0.498	4980	0.62	12.9	4450	730	42	353	62	40	1.6	11.0	25	0.01
KL34-08	334.8	337.8	0.194	1940	0.38	6.1	16100	163	38	29	17	41	1.5	8.5	20	0.01
KL34-08	337.8	340.8	0.31	3100	0.48	7.7	18900	209	59	32	38	11	1.1	15.5	30	0.01
KL34-08	340.8	343.8	0.85	8500	1.46	24.6	12900	168	42	142	40	82	2.9	20.0	57	0.01
KL34-08	343.8	346.8	1.05	10500	0.73	24.1	1260	314	35	521	17	21	2	22.5	52	0.01
KL34-08	346.8	349.8	0.31	3100	0.43	5.8	1230	337	110	14	7	36	1.9	6.5	24	0.01
KL34-08	349.8	352.8	1.27	12700	1.31	9.3	9300	316	100	36	62	33	1.5	60.5	33	0.01
KL34-08	352.8	355.8	1.62	16200	1.99	4.6	105	83	36	19	64	12	0.6	106.0	36	0.01
KL34-08	355.8	360.8	1.06	10600	1.88	4	209	102	42	17	46	12	0.5	102.5	34	0.01
KL34-08	360.8	363.8	0.64	6400	1.54	3.8	368	146	60	21	70	15	0.3	100.0	42	0.01
KL34-08	363.8	365.8	1.08	10800	1.63	5.8	820	176	31	14	76	15	0.2	120.0	39	0.01
KL34-08	365.8	369.7	2.56	25600	1.33	9.7	3500	560	12	2	21	72	2.4	30.0	119	0.01
KL34-08	369.7	373.4	1.72	17200	1.21	17.8	5600	920	25	2	26	38	0.6	33.0	138	0.01
KL34-08	373.4	376.4	2.28	22800	1.43	4.9	162	45	15	4	19	37	0.4	35.0	184	0.01
KL34-08	376.4	379.4	2.61	26100	2.01	10.3	450	171	13	85	3	37	2.4	48.0	191	0.01
KL34-08	379.4	382.7	1.43	14300	1.01	27.7	410	670	32	68	9	15	4.5	23.0	126	0.01
KL34-08	382.7	385.8	1.09	10900	0.26	9.2	2130	1450	28	338	2	10	2.5	9.5	126	0.28
KL34-08	385.8	388.8	0.59	5900	0.3	2.7	850	348	9	189	4	9	0.6	16.0	65	0.01
KL34-08	388.8	391.8	0.64	6400	0.34	2.9	278	226	4	139	2	12	0.5	10.0	66	0.01
KL34-08	391.8	394.8	0.67	6700	0.33	2.8	91	31	6	79	2	10	0.3	6.8	77	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL34-08	394.8	397.8	0.26	2600	0.22	3.1	264	231	16	197	10	3	0.8	3.8	79	0.01
KL34-08	397.8	400.8	0.68	6800	0.29	2.2	185	101	5	42	3	10	0.3	6.0	73	0.01
KL34-08	400.8	403.8	0.67	6700	0.32	3.1	329	145	20	80	4	11	1.3	6.8	50	0.01
KL34-08	403.8	406.8	0.511	5110	0.26	3	760	316	5	29	3	10	1	4.8	113	0.01
KL34-08	406.8	409.8	0.34	3400	0.22	2.3	192	97	7	18	2	7	0.7	2.8	87	0.01
KL34-08	409.8	412.8	0.62	6200	0.28	1.6	95	16	2	28	1	9	0.01	4.9	100	0.01
KL34-08	412.8	415.8	0.461	4610	0.26	1.1	104	18	2	10	1	10	0.2	5.3	104	0.01
KL34-08	415.8	418.8	0.474	4740	0.39	1.5	309	22	6	15	2	12	0.01	5.5	99	0.01
KL34-08	418.8	421.8	0.354	3540	0.34	1.8	116	45	5	58	1	11	0.01	6.1	97	0.01
KL34-08	421.8	424.8	0.421	4210	0.28	1.5	99	17	2	18	1	10	0.01	3.8	97	0.01
KL34-08	424.8	427.8	0.64	6400	0.45	1.9	100	26	3	17	2	12	0.01	4.0	108	0.01
KL34-08	427.8	430.8	0.6	6000	0.37	1.5	62	9	1	18	0.01	10	0.6	3.8	92	0.01
KL34-08	430.8	433.8	0.92	9200	0.74	1.7	57	26	1	21	0.01	10	0.2	3.5	104	0.01
KL34-08	433.8	436.8	0.61	6100	0.36	1.5	65	27	1	10	0.01	12	0.01	3.8	89	0.01
KL34-08	436.8	439.8	0.95	9500	0.51	1.7	1080	74	4	7	0.01	11	0.01	5.4	109	0.01
KL34-08	439.8	442.8	1.44	14400	0.92	2.7	120	40	1	28	0.01	15	0.01	8.5	90	0.01
KL34-08	442.8	445.8	1.18	11800	0.58	2.3	98	24	2	12	0.01	16	0.01	7.0	81	0.01
KL34-08	445.8	448.8	1.45	14500	0.85	2.2	78	36	2	7	0.01	16	0.2	10.0	113	0.01
KL34-08	448.8	452.7	1.74	17400	0.77	3	115	18	0.01	67	1	15	0.01	7.5	52	0.01
KL34-08	452.7	454.8	1.05	10500	0.45	1.5	73	30	1	10	0.01	10	0.01	6.5	59	0.01
KL34-08	454.8	457.8	0.6	6000	0.14	1.7	46	57	1	41	1	4	0.4	3.0	197	0.01
KL34-08	457.8	460.8	0.379	3790	0.08	2	22	19	0.01	104	2	2	0.01	1.8	235	0.01
KL34-08	460.8	463.8	0.447	4470	0.16	4.1	69	82	8	59	5	3	1.5	2.8	76	0.01
KL34-08	463.8	466.8	0.69	6900	0.33	7.8	131	77	5	50	27	4	4.4	3.3	250	0.01
KL34-08	466.8	469.8	0.184	1840	0.33	3.4	450	1090	470	60	4	4	2.5	5.3	219	0.01
KL34-08	469.8	472.8	0.411	4110	0.31	2.9	292	76	5	40	2	3	2.1	4.3	225	0.01
KL34-08	472.8	474.8	0.434	4340	0.5	2.7	35	43	5	48	10	9	2.8	4.3	167	0.01
KL34-08	474.8	477.8	1.04	10400	0.58	3.5	30	24	3	36	7	6	0.4	6.0	29	0.01
KL34-08	477.8	480.8	0.281	2810	0.52	4.6	39	54	1	37	7	10	0.6	8.4	198	0.01
KL34-08	480.8	483.8	0.458	4580	0.12	4.8	560	620	48	17	50	7	1.9	6.5	202	0.01
KL34-08	483.8	486.8	0.22	2200	0.42	5.8	3070	3020	540	82	3	1	7	2.3	298	0.01
KL34-08	486.8	489.8	0.33	3300	0.18	2.6	660	590	420	54	5	3	4.4	3.5	262	0.01
KL34-08	489.8	492.8	0.3	3000	0.16	2.1	45	75	18	87	3	2	7.3	3.7	276	0.01
KL34-08	492.8	495.8	0.372	3720	0.16	2.4	220	78	33	24	1	1	1.4	4.8	40	0.01
KL34-08	495.8	498.8	0.535	5350	0.29	1.7	181	75	8	23	5	3	1.3	3.7	264	0.01
KL34-08	498.8	501.8	0.27	2700	0.23	1.1	21	13	1	36	2	2	0.01	2.8	263	0.01
KL34-08	501.8	504.8	0.404	4040	0.38	1.4	22	20	2	33	4	2	0.01	2.5	254	0.01
KL34-08	504.8	507.8	0.75	7500	0.52	1.9	40	41	10	41	3	4	3.4	2.3	228	0.01
KL34-08	507.8	510.8	0.421	4210	0.51	1.7	27	17	2	56	3	3	0.9	3.5	70	0.01
KL34-08	510.8	513.8	0.23	2300	0.2	0.9	17	12	1	46	2	3	0.2	1.8	88	0.01
KL34-08	513.8	516.8	0.27	2700	0.2	1.1	23	29	20	35	2	5	10.5	4.5	228	0.01
KL34-08	516.8	519.8	0.33	3300	0.49	0.8	26	24	8	20	2	3	4.7	2.5	321	0.01
KL34-08	519.8	522.8	0.24	2400	0.15	0.8	21	34	11	16	1	1	0.01	2.3	140	0.01
KL34-08	522.8	526.2	0.33	3300	0.4	0.9	29	27	5	15	3	2	0.01	3.1	219	0.01
KL34-09	0	4	0.0041	41	0.01	0.1	122	46	4	3	0.01	1	0.9	0.9	24	0.01
KL34-09	4	6.9	0.0162	162	0.02	0.1	128	63	5	5	0.01	1	1.7	1.8	26	0.01
KL34-09	6.9	10.4	0.0102	102	0.03	0.1	208	88	10	6	0.01	1	2.4	2.1	28	0.01
KL34-09	10.4	13.2	0.0077	77	0.04	0.1	216	91	13	7	0.01	1	2.6	1.8	31	0.01
KL34-09	13.2	17.2	0.0087	87	0.02	0.1	102	40	11	4	0.01	1	0.7	1.0	21	0.01
KL34-09	17.2	20.7	0.0061	61	0.01	0.1	216	85	5	6	0.01	1	0.3	0.9	20	0.01
KL34-09	20.7	23.7	0.0353	353	0.03	0.1	231	109	7	5	0.01	1	1	1.1	23	0.01
KL34-09	23.7	26.7	0.0041	41	0.01	0.1	191	110	6	4	0.01	1	1.2	1.3	27	0.01
KL34-09	26.7	29.3	0.0084	84	0.02	0.1	175	91	6	4	0.01	1	0.4	0.9	25	0.01
KL34-09	29.3	32.4	0.0042	42	0.03	0.1	161	60	6	3	0.01	1	0.7	1.3	18	0.01
KL34-09	32.4	34.4	0.0029	29	0.02	0.1	168	73	7	4	0.01	1	0.3	1.3	16	0.01
KL34-09	34.4	37.1	0.0049	49	0.09	1.1	266	120	28	6	0.01	1	2.2	3.8	76	0.01
KL34-09	37.1	39.4	0.0128	128	0.02	1	400	364	10	3	1	1	0.8	1.1	35	0.01
KL34-09	39.4	42.8	0.0145	145	0.05	0.8	287	187	11	5	1	1	0.5	1.1	34	0.01
KL34-09	42.8	45.4	0.0097	97	0.04	0.1	125	72	5	2	0.01	1	0.5	0.8	30	0.01
KL34-09	45.4	47.7	0.0138	138	0.02	0.1	117	32	10	3	0.01	1	0.5	0.7	34	0.01
KL34-09	47.7	50.7	0.0051	51	0.02	0.1	342	326	14	5	0.01	1	0.6	3.2	21	0.01
KL34-09	50.7	53.7	0.0046	46	0.07	0.1	157	63	11	2	0.01	1	0.6	1.7	19	0.01
KL34-09	53.7	56.7	0.0112	112	0.42	5.6	6500	1600	55	3	1	1	15.3	6.8	22	1.08

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL34-09	56.7	59.7	0.0347		347	0.03	0.7	229	96	5	4	0.01	1	0.2	1.2	16	0.01
KL34-09	59.7	62.7	0.011		110	0.03	1.1	343	271	19	3	0.01	1	1	1.3	13	0.01
KL34-09	62.7	65.7	0.0108		108	0.03	0.1	322	232	16	4	0.01	1	0.8	1.8	12	0.01
KL34-09	65.7	68	0.0196		196	0.4	4	2780	1300	78	16	1	1	9.8	5.2	18	0.2
KL34-09	68	71.7	0.0173		173	0.03	0.9	394	276	16	2	0.01	1	0.4	1.2	16	0.01
KL34-09	71.7	74.7	0.0096		96	0.03	3.1	1860	2010	28	3	0.01	1	4.3	6.5	19	0.01
KL34-09	74.7	77.7	0.0132		132	0.02	1.1	460	361	11	2	0.01	1	0.6	2.2	19	0.01
KL34-09	77.7	80.7	0.0053		53	0.01	0.8	770	231	10	3	0.01	1	0.3	1.3	14	0.01
KL34-09	80.7	83.7	0.0038		38	0.02	0.9	760	384	9	4	0.01	1	0.3	1.5	15	0.01
KL34-09	83.7	86.7	0.0064		64	0.06	1.7	1480	1000	22	5	0.01	1	1.4	4.0	24	0.01
KL34-09	86.7	89.7	0.0036		36	0.03	1	580	206	14	4	0.01	1	0.5	2.3	21	0.01
KL34-09	89.7	92.7	0.0167		167	0.2	6.7	9100	5600	43	3	5	1	9.8	8.0	17	0.35
KL34-09	92.7	95.4	0.0317		317	0.12	0.9	950	470	10	5	0.01	1	0.8	2.5	17	0.01
KL34-09	95.4	98.5	0.0092		92	0.04	1.2	980	670	21	4	0.01	1	1.5	4.5	35	0.01
KL34-09	98.5	101.6	0.0078		78	0.01	0.1	32	31	12	2	0.01	1	0.01	1.5	34	0.01
KL34-09	101.6	104.7	0.048		480	0.07	0.9	770	420	26	2	0.01	1	0.5	2.0	17	0.01
KL34-09	104.7	107.2	0.0028		28	0.03	0.8	900	590	4	2	0.01	1	0.7	2.1	12	0.01
KL34-09	107.2	110.4	0.0097		97	0.03	0.9	1310	670	5	2	0.01	1	1.9	2.2	13	0.01
KL34-09	110.4	113.5	0.0286		286	0.08	1.2	1450	1120	11	3	0.01	1	1.9	5.4	14	0.01
KL34-09	113.5	116.6	0.0056		56	0.01	0.7	830	510	4	4	0.01	1	0.01	2.1	13	0.01
KL34-09	116.6	119.7	0.0148		148	0.03	1.2	1480	960	10	7	0.01	1	0.3	2.6	31	0.01
KL34-09	119.7	122.5	0.0323		323	0.05	2.8	7600	2500	5	4	0.01	1	2.5	6.5	27	0.1
KL34-09	122.5	125.6	0.0057		57	0.01	0.9	790	590	10	6	0.01	1	1.2	1.3	16	0.01
KL34-09	125.6	128.6	0.008		80	0.01	0.7	620	780	15	8	0.01	1	1.8	2.3	18	0.01
KL34-09	128.6	131.7	0.0084		84	0.01	1.4	750	930	14	8	2	1	1.3	2.4	14	0.01
KL34-09	131.7	133.9	0.0075		75	0.01	0.6	1070	500	8	7	0.01	1	1.2	3.4	14	0.01
KL34-09	133.9	137	0.043		430	0.07	5	2460	2830	110	8	6	1	6	14.4	15	0.01
KL34-09	137	140.1	0.297		2970	0.02	4.1	1950	1350	70	25	6	1	3	11.8	20	0.01
KL34-09	140.1	143.7	0.042		420	0.01	12.8	1670	2400	52	18	31	1	4.8	5.3	17	0.01
KL34-09	143.7	146.7	0.094		940	0.02	5	1600	710	110	30	18	2	5.2	2.2	16	0.01
KL34-09	146.7	149.7	0.0315		315	0.01	3.8	990	500	48	17	10	1	1.4	2.5	17	0.01
KL34-09	149.7	152.7	0.0292		292	0.01	5.3	3340	2360	44	35	15	1	1.3	5.3	15	0.01
KL34-09	152.7	155.7	0.21		2100	0.02	32.2	17100	11600	100	173	54	1	8.5	25.8	19	0.14
KL34-09	155.7	158.4	0.046		460	0.01	2.6	780	860	51	35	7	1	2.2	2.8	16	0.01
KL34-09	158.4	161.1	0.0298		298	0.01	1.6	640	560	67	84	8	1	1.8	1.3	17	0.01
KL34-09	161.1	164.2	0.153		1530	0.09	1.9	910	450	110	293	22	2	2.3	2.5	19	0.01
KL34-09	164.2	167.2	0.082		820	0.02	1.7	600	630	40	603	12	1	1.7	4.0	27	0.01
KL34-09	167.2	170.5	0.282		2820	0.12	2	680	640	100	449	8	6	1.3	3.5	18	0.01
KL34-09	170.5	173.6	0.104		1040	0.02	6.4	8600	6800	96	74	16	1	2.5	4.9	29	0.01
KL34-09	173.6	176.7	0.045		450	0.01	2.4	1190	990	31	440	8	1	1.2	1.7	22	0.01
KL34-09	176.7	179.7	0.066		660	0.03	4.5	3480	2400	50	251	15	1	2.4	5.5	26	0.01
KL34-09	179.7	182.7	0.067		670	0.02	9.4	21200	14100	42	114	13	1	7.8	18.2	24	0.1
KL34-09	182.7	185.7	0.084		840	0.07	2.7	3140	1600	75	112	21	3	1.2	7.8	21	0.01
KL34-09	185.7	188.1	0.085		850	0.02	5.2	2470	2450	81	139	54	2	1.3	15.7	40	0.01
KL34-09	188.1	191.7	0.139		1390	0.06	6.1	1620	2370	48	510	36	4	6.8	12.3	60	0.01
KL34-09	191.7	194.7	0.092		920	0.03	2.7	2090	1350	47	520	23	2	2.5	7.5	54	0.01
KL34-09	194.7	197.5	0.067		670	0.03	1.4	1510	450	70	129	14	1	3.3	4.1	43	0.01
KL34-09	197.5	200.6	0.115		1150	0.06	2	4050	940	100	296	44	4	5.7	13.8	57	0.01
KL34-09	200.6	203.2	0.085		850	0.04	2.4	8300	2700	51	124	40	6	4.3	17.5	44	0.01
KL34-09	203.2	206.7	0.198		1980	0.07	2.7	2500	1320	56	415	33	7	3.3	17.8	58	0.01
KL34-09	206.7	210.1	0.161		1610	0.04	1.6	4050	720	74	99	9	5	1.9	13.0	41	0.01
KL34-09	210.1	213.6	3.1		31000	0.16	33.4	13100	4600	520	173	71	14	10.5	56.0	67	0.1
KL34-09	213.6	215.7	0.79		7900	0.13	7	6300	1000	84	55	15	10	9.3	15.8	50	0.01
KL34-09	215.7	218.7	0.185		1850	0.1	1.7	2780	139	120	7	8	2	1.8	8.8	25	0.01
KL34-09	218.7	221.7	0.059		590	0.05	0.8	1090	630	42	9	6	1	3	10.0	26	0.01
KL34-09	221.7	224.7	0.101		1010	0.03	0.7	1190	104	50	2	13	2	2.3	3.8	30	0.01
KL34-09	224.7	227.7	0.053		530	0.17	0.7	1370	119	120	10	2	3	1.4	3.0	43	0.01
KL34-09	227.7	230.7	0.08		800	0.6	1	1080	85	200	15	1	3	3.3	1.5	38	0.01
KL34-09	230.7	232.8	0.32		3200	0.33	1.1	8000	62	130	14	2	36	2.3	12.5	60	0.01
KL34-09	232.8	235.9	0.166		1660	0.15	1.4	6100	70	120	13	1	24	0.5	4.8	44	0.01
KL34-09	235.9	239	0.154		1540	0.14	1	3020	51	110	11	1	10	0.2	2.3	29	0.01
KL34-09	239	242.1	0.201		2010	0.32	1.4	1520	47	91	81	4	15	1	5.5	124	0.01
KL34-09	242.1	245.2	0.79		7900	0.24	1.8	257	184	27	89	4	16	1	19.3	115	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL34-09	245.2	248.4	0.56	5600	0.08	0.7	133	129	7	95	4	15	0.5	17.5	99	0.01
KL34-09	248.4	251.5	0.21	2100	0.18	0.8	134	43	13	88	2	10	0.6	5.5	62	0.01
KL34-09	251.5	253.8	0.459	4590	0.12	1.8	126	65	9	22	3	12	0.6	9.4	68	0.01
KL34-09	253.8	256.8	0.24	2400	0.11	0.9	100	79	14	149	5	17	0.7	3.2	99	0.01
KL34-09	256.8	258.5	0.088	880	0.04	0.1	176	84	9	130	1	12	0.4	4.5	136	0.01
KL34-09	258.5	262.6	0.132	1320	0.07	1.2	285	139	20	75	1	15	0.7	1.9	42	0.01
KL34-09	262.6	265.7	0.22	2200	0.16	5.6	10800	1670	41	42	4	13	6.6	12.4	186	0.01
KL34-09	265.7	268.9	0.22	2200	0.14	2.4	860	319	15	31	4	12	2.1	8.8	54	0.01
KL34-09	268.9	272	0.21	2100	0.11	1.4	283	200	14	34	5	9	1.4	4.0	40	0.01
KL34-09	272	275.1	0.41	4100	0.19	7.8	12000	5600	35	41	3	11	6.9	11.0	115	0.01
KL34-09	275.1	278.7	0.378	3780	0.3	3.7	920	590	31	15	3	15	1.6	6.0	128	0.01
KL34-09	278.7	281.7	0.093	930	0.08	3.6	1320	2530	12	53	1	11	2.8	7.0	98	0.01
KL34-09	281.7	284.7	0.29	2900	0.19	1.7	364	136	28	102	3	17	1.2	7.0	45	0.01
KL34-09	284.7	287.7	0.21	2100	0.17	1.2	245	127	14	54	1	8	0.5	3.0	35	0.01
KL34-09	287.7	290.7	0.28	2800	0.12	1.6	193	133	12	21	3	12	1	6.3	137	0.01
KL34-09	290.7	293.7	0.23	2300	0.11	2.3	55	70	6	4	5	13	0.8	7.5	58	0.01
KL34-09	293.7	296.7	0.39	3900	0.16	4.2	80	127	11	7	5	11	1.3	6.3	21	0.01
KL34-09	296.7	299.7	0.424	4240	0.11	4.6	155	137	20	80	4	12	1	10.8	45	0.01
KL34-09	299.7	302.7	0.67	6700	0.16	6	248	207	15	71	2	38	1.9	11.8	50	0.01
KL34-09	302.7	305.7	0.449	4490	0.11	3.5	145	235	18	97	2	16	0.8	9.0	93	0.01
KL34-09	305.7	308.7	0.56	5600	0.23	20.8	16500	6800	27	102	16	16	5.4	7.5	29	0.01
KL34-09	308.7	311.7	1.01	10100	0.37	18.3	670	610	19	203	13	12	1.7	10.0	66	0.01
KL34-09	311.7	314.7	1.06	10600	0.23	7.3	332	680	30	479	3	10	3	8.0	120	0.01
KL34-09	314.7	316.7	2.57	25700	0.68	4.5	540	126	35	284	2	55	6.9	11.0	110	0.01
KL34-09	316.7	320.7	0.066	660	0.05	0.1	2910	54	43	21	1	14	1.4	1.0	54	0.01
KL34-09	320.7	323.7	0.0345	345	0.01	0.7	480	183	50	224	3	1	0.5	2.3	26	0.01
KL34-09	323.7	326.7	0.219	2190	0.12	1.2	4830	71	58	23	4	20	2.7	3.3	25	0.01
KL34-09	326.7	329.3	0.096	960	0.06	0.8	930	770	30	10	1	5	1	1.8	29	0.01
KL34-09	329.3	331.7	0.32	3200	0.2	1	1310	119	53	6	1	9	1.8	4.3	18	0.01
KL34-09	331.7	333	1.83	18300	0.78	14.6	850	82	150	70	9	28	3.8	30.0	36	0.01
KL34-09	333	335.5	0.35	3500	0.12	2.3	420	213	11	374	1	8	0.01	5.4	52	0.01
KL34-09	335.5	338.7	0.053	530	0.04	0.9	236	151	3	234	1	1	0.3	1.0	31	0.01
KL34-09	338.7	341.1	0.067	670	0.09	0.7	133	108	1	258	0.01	1	0.2	1.5	57	0.01
KL34-09	341.1	343.2	0.59	5900	0.42	4.1	256	121	9	312	3	6	0.2	5.5	21	0.01
KL34-09	343.2	347.1	1.61	16100	0.78	4.1	3200	69	90	65	4	65	2.1	7.0	25	0.01
KL34-09	347.1	349.4	0.83	8300	0.89	4.2	1400	135	210	195	24	40	3	5.0	29	0.01
KL34-09	349.4	351.8	1.52	15200	3.56	12.3	3400	138	180	25	46	56	1.6	28.0	38	0.01
KL34-09	351.8	354.1	3.22	32200	2.42	5.7	730	103	540	129	3	10	4.1	8.0	68	0.01
KL34-09	354.1	356.1	1.75	17500	1.04	2.2	390	54	61	109	3	15	2.3	5.0	28	0.01
KL34-09	356.1	358.8	0.98	9800	1.44	2.4	318	28	200	29	4	18	3.3	4.0	22	0.01
KL34-09	358.8	361.2	1.43	14300	1.3	5.1	1230	228	100	41	30	19	1.2	17.3	63	0.01
KL34-09	361.2	364.3	2.15	21500	1.7	9.7	1220	226	150	29	32	81	3.7	13.0	53	0.01
KL34-09	364.3	366.6	0.86	8600	1.74	3	1590	149	200	27	5	25	2.1	6.8	28	0.01
KL34-09	366.6	369	1.53	15300	2.12	3.2	358	64	180	13	22	19	1.6	18.5	27	0.01
KL34-09	369	372.3	1.95	19500	2.3	6.2	9200	114	38	34	4	15	0.5	24.0	31	0.01
KL34-09	372.3	375	1.22	12200	0.8	11.5	4900	305	14	264	2	19	0.9	26.0	35	0.01
KL34-09	375	377.7	0.71	7100	0.24	5.1	740	214	15	108	2	7	1.3	8.0	75	0.01
KL34-09	377.7	379.8	0.406	4060	0.21	2.9	115	27	2	29	1	7	0.2	4.8	14	0.01
KL34-09	379.8	382.3	0.18	1800	0.1	1.4	90	31	5	35	1	3	0.7	1.8	23	0.01
KL34-09	382.3	384.7	0.21	2100	0.12	1.4	80	31	4	75	0.01	5	0.5	3.0	40	0.01
KL34-09	384.7	388	0.47	4700	0.38	2	165	43	8	176	0.01	7	0.6	3.5	16	0.01
KL34-09	388	389.7	0.3	3000	0.19	0.8	131	34	9	165	0.01	10	0.5	4.8	21	0.01
KL34-09	389.7	392.7	0.33	3300	0.23	0.7	124	35	8	48	0.01	7	0.3	3.3	25	0.01
KL34-09	392.7	395.7	1.54	15400	0.91	1.7	229	11	3	24	0.01	33	0.01	9.0	24	0.01
KL34-09	395.7	398.7	1.29	12900	0.72	1.9	310	16	4	99	0.01	42	0.01	1.0	60	0.01
KL34-09	398.7	401.7	0.459	4590	0.26	0.9	359	68	12	76	0.01	13	0.4	4.5	19	0.01
KL34-09	401.7	404.7	0.321	3210	0.17	1.4	95	45	4	12	0.01	6	0.01	1.3	18	0.01
KL34-09	404.7	406.9	1.28	12800	0.75	1.9	201	15	3	8	0.01	11	0.01	8.5	19	0.01
KL34-09	406.9	410.1	0.489	4890	0.26	1	117	46	1	10	0.01	6	0.01	3.3	13	0.01
KL34-09	410.1	413.2	0.15	1500	0.1	0.1	146	48	4	9	0.01	6	0.01	1.3	17	0.01
KL34-09	413.2	416.3	0.16	1600	0.09	0.1	190	33	3	8	1	11	0.01	1.8	13	0.01
KL34-09	416.3	419.5	0.28	2800	0.15	0.1	134	16	5	13	0.01	10	0.01	1.8	17	0.01
KL34-09	419.5	422.6	0.408	4080	0.19	1.1	97	21	6	5	0.01	8	0.01	3.3	14	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL34-09	422.6	425.7	0.28	2800	0.2	0.9	161	26	7	14	0.01	7	0.01	3.8	16	0.01
KL34-09	425.7	428.7	0.435	4350	0.43	1.5	183	26	3	214	0.01	8	0.01	2.8	10	0.01
KL34-09	428.7	431.8	0.81	8100	0.46	2.4	361	12	5	9	0.01	16	0.01	5.8	20	0.01
KL34-09	431.8	434.7	0.91	9100	0.76	3.9	840	13	8	6	1	22	0.2	7.0	14	0.01
KL34-09	434.7	437.7	0.35	3500	0.28	2.4	5400	13	11	5	4	55	1.4	6.5	14	0.01
KL34-09	437.7	440.7	0.3	3000	0.3	1.8	324	8	12	7	1	21	0.8	5.3	14	0.01
KL34-09	440.7	443.7	0.29	2900	0.11	1.3	146	14	2	6	1	3	0.01	2.5	9	0.01
KL34-09	443.7	446.7	0.392	3920	0.41	1	130	10	2	17	0.01	4	0.01	2.8	7	0.01
KL34-09	446.7	449.7	0.1	1000	0.08	0.8	141	8	14	26	0.01	4	0.2	1.8	17	0.01
KL34-09	449.7	452.7	0.115	1150	0.06	0.7	84	13	12	6	0.01	5	0.2	2.8	14	0.01
KL34-09	452.7	455.7	0.141	1410	0.1	0.1	45	9	1	20	0.01	2	0.3	1.5	23	0.01
KL34-09	455.7	458.7	0.21	2100	0.2	1.1	57	13	1	31	0.01	2	0.01	2.3	16	0.01
KL34-09	458.7	461.7	0.22	2200	0.3	1.4	64	15	8	279	6	5	0.5	22.5	87	0.01
KL34-09	461.7	464.7	0.72	7200	0.4	2.7	430	218	16	98	3	38	1.3	24.8	87	0.01
KL34-09	464.7	467.7	0.69	6900	0.59	2.4	136	15	12	89	3	13	0.01	8.3	25	0.01
KL34-09	467.7	470.7	0.35	3500	0.25	1.2	192	53	9	57	0.01	15	0.6	9.3	19	0.01
KL34-09	470.7	473.7	0.81	8100	0.48	2	393	120	4	20	0.01	20	0.01	7.8	34	0.01
KL34-09	473.7	476.7	0.61	6100	0.49	1.1	123	22	5	20	0.01	14	0.2	6.3	30	0.01
KL34-09	476.7	479.7	0.24	2400	0.13	0.9	58	16	3	23	0.01	7	0.01	3.5	24	0.01
KL34-09	479.7	482.7	0.138	1380	0.08	0.1	84	53	2	17	0.01	7	0.01	2.3	29	0.01
KL34-09	482.7	485.7	0.64	6400	0.27	1	64	11	3	16	0.01	9	0.01	6.3	30	0.01
KL34-09	485.7	488.7	0.56	5600	0.22	0.7	123	25	1	28	0.01	15	1.5	5.0	42	0.01
KL34-09	488.7	491.7	1.61	16100	0.57	1.9	127	8	0.01	21	0.01	23	0.01	12.5	32	0.01
KL34-09	491.7	494.7	0.59	5900	0.32	1	100	9	1	18	0.01	20	0.01	4.0	23	0.01
KL34-09	494.7	497.7	1.76	17600	0.97	2.1	120	10	0.01	28	0.01	30	0.01	12.5	28	0.01
KL34-09	497.7	500.7	2.55	25500	1.19	3	128	11	0.01	31	0.01	33	0.01	14.5	17	0.01
KL34-09	500.7	503.7	1.41	14100	0.7	2	127	9	0.01	22	0.01	31	0.01	15.7	22	0.01
KL34-09	503.7	506.7	1.74	17400	0.76	1.7	134	6	0.01	9	0.01	37	0.01	13.5	14	0.01
KL34-09	506.7	509.7	1.05	10500	0.56	1.2	110	9	0.01	24	0.01	31	0.01	8.5	17	0.01
KL34-09	509.7	511.7	0.6	6000	0.29	0.9	84	9	0.01	12	0.01	29	0.01	6.0	16	0.01
KL34-09	511.7	514.7	1.4	14000	0.64	1.5	80	10	0.01	21	0.01	31	0.01	6.0	19	0.01
KL34-09	514.7	517.7	1.23	12300	0.53	1.1	87	5	0.01	83	0.01	29	0.01	10.8	18	0.01
KL34-09	517.7	520.7	1.13	11300	0.53	1.1	93	8	0.01	8	0.01	33	0.01	8.0	18	0.01
KL34-09	520.7	523.7	1.37	13700	0.73	1.4	103	5	0.01	8	0.01	35	0.01	13.0	22	0.01
KL34-09	523.7	526.7	1.35	13500	0.6	1.2	90	7	0.01	6	0.01	37	0.01	11.5	17	0.01
KL34-09	526.7	529.7	0.6	6000	0.34	0.8	48	10	0.01	20	0.01	23	0.01	7.1	117	0.01
KL34-09	529.7	532.7	0.87	8700	0.35	1.1	72	9	3	19	0.01	26	0.01	8.9	63	0.01
KL34-09	532.7	535.7	1.44	14400	1.28	1.3	78	14	0.01	8	0.01	23	0.01	11.5	97	0.01
KL34-09	535.7	538.7	1.29	12900	0.62	0.8	59	7	1	22	0.01	22	0.01	7.5	23	0.01
KL34-09	538.7	541.7	1.63	16300	0.63	1.3	73	5	1	48	0.01	23	0.01	8.5	17	0.01
KL34-09	541.7	544.7	1.18	11800	0.57	1.1	79	6	2	17	0.01	38	0.01	9.0	27	0.01
KL34-09	544.7	547.7	1.4	14000	0.72	1.6	86	7	0.01	27	0.01	50	0.01	5.7	15	0.01
KL34-09	547.7	550.7	1.57	15700	0.73	2	93	5	1	63	0.01	52	0.01	9.5	26	0.01
KL34-09	550.7	553.7	1.61	16100	0.78	2.5	91	8	2	32	0.01	47	0.01	10.0	32	0.01
KL34-09	553.7	556.7	2.34	23400	1.16	2.9	94	5	2	4	0.01	64	0.01	11.0	36	0.01
KL34-09	556.7	559.7	2.13	21300	1.04	2.7	91	9	0.01	110	0.01	48	0.01	11.0	27	0.01
KL34-09	559.7	562.7	1.81	18100	0.89	2.4	96	8	0.01	39	0.01	54	0.01	15.0	31	0.01
KL34-09	562.7	565.7	1.74	17400	0.76	1.8	98	9	0.01	45	0.01	56	0.01	18.2	39	0.01
KL34-09	565.7	568.7	1.07	10700	0.64	1.1	83	8	0.01	70	0.01	53	0.01	9.3	30	0.01
KL34-09	568.7	571.7	1.31	13100	0.75	1.5	87	8	0.01	22	0.01	53	0.01	9.0	40	0.01
KL34-09	571.7	574.7	1.2	12000	0.68	1.4	117	11	1	7	0.01	59	0.01	5.5	28	0.01
KL34-09	574.7	577.7	0.96	9600	0.57	1	135	9	1	34	0.01	48	0.01	4.0	35	0.01
KL34-09	577.7	580.7	1.24	12400	0.71	1.4	189	13	1	39	0.01	56	0.01	7.5	21	0.01
KL34-09	580.7	583.7	1.44	14400	0.94	1.3	274	12	0.01	71	0.01	59	0.01	8.5	43	0.01
KL34-09	583.7	586.7	0.416	4160	0.24	0.7	114	13	0.01	7	0.01	52	0.01	6.8	32	0.01
KL34-09	586.7	589.7	0.21	2100	0.13	0.6	97	10	0.01	28	0.01	48	0.01	4.3	29	0.01
KL34-09	589.7	592.7	0.32	3200	0.24	0.1	520	9	1	12	0.01	61	0.01	5.0	28	0.01
KL34-09	592.7	595.7	0.3	3000	0.18	0.1	110	10	2	25	0.01	43	0.01	4.3	32	0.01
KL34-09	595.7	598.7	0.57	5700	0.36	1	100	18	1	23	0.01	49	0.01	5.3	43	0.01
KL34-09	598.7	601.7	0.85	8500	0.41	1	83	9	0.01	31	1	68	0.01	5.6	33	0.01
KL34-09	601.7	604.7	0.92	9200	0.64	1.5	110	10	0.01	8	0.01	69	0.01	9.8	38	0.01
KL34-09	604.7	607.7	1.07	10700	0.53	1.3	79	6	0.01	32	0.01	70	0.01	10.5	39	0.01
KL34-09	607.7	610.7	1.11	11100	0.63	1.8	87	6	2	4	0.01	58	0.01	10.5	33	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL34-09	610.7	613.7	1.03	10300	0.45	1.1	125	8	1	101	2	77	0.01	11.6	68	0.01
KL34-09	613.7	616.7	1.12	11200	0.68	1.3	140	6	2	61	0.01	63	0.01	14.5	60	0.01
KL34-09	616.7	619.7	0.63	6300	0.34	0.9	100	6	1	6	0.01	63	0.01	8.0	61	0.01
KL34-09	619.7	622.1	0.59	5900	0.32	1	109	6	1	22	1	81	0.01	7.6	52	0.01
KL34-09	622.1	625.1	0.96	9600	0.51	1.1	148	8	3	10	0.01	65	0.01	8.8	37	0.01
KL34-09	625.1	628.2	1.3	13000	0.61	2	221	40	0.01	7	1	63	0.01	12.5	36	0.01
KL34-09	628.2	631.3	1.03	10300	0.45	1.2	431	79	0.01	11	0.01	61	0.01	10.0	43	0.01
KL34-09	631.3	634.1	1.43	14300	0.9	2.3	1170	271	0.01	290	1	80	0.01	8.7	54	0.01
KL34-09	634.1	637.3	0.91	9100	0.43	1.1	217	11	0.01	42	1	38	0.01	6.0	51	0.01
KL34-09	637.3	640.4	0.42	4200	0.23	1	192	22	1	105	0.01	46	0.01	4.0	77	0.01
KL34-09	640.4	643.6	0.23	2300	0.16	0.1	195	12	0.01	6	0.01	50	0.01	2.3	52	0.01
KL34-09	643.6	646.7	0.9	9000	0.47	1.4	391	187	1	8	0.01	55	0.01	7.0	23	0.01
KL34-09	646.7	649.7	0.7	7000	0.39	1.1	200	12	0.01	10	0.01	54	0.01	4.0	43	0.01
KL34-09	649.7	652.7	0.61	6100	0.34	1	235	8	0.01	7	0.01	47	0.01	5.0	31	0.01
KL34-09	652.7	655.7	0.64	6400	0.49	1.3	196	6	0.01	16	0.01	82	0.01	9.3	21	0.01
KL34-09	655.7	658.7	1.21	12100	0.7	1.7	285	11	1	8	0.01	76	0.01	9.0	43	0.01
KL34-09	658.7	661.7	0.49	4900	0.25	1.2	234	6	2	220	0.01	46	0.01	7.0	41	0.01
KL34-09	661.7	664.7	0.46	4600	0.22	1	187	8	0.01	11	0.01	65	0.01	6.9	37	0.01
KL34-09	664.7	667.7	0.53	5300	0.21	1.1	193	6	1	6	0.01	54	0.01	7.5	41	0.01
KL34-09	667.7	670.7	0.2	2000	0.11	0.6	154	7	1	6	0.01	64	0.01	5.0	43	0.01
KL34-09	670.7	673.7	0.27	2700	0.15	0.7	168	6	1	9	0.01	49	0.01	4.5	59	0.01
KL34-09	673.7	676.7	0.24	2400	0.16	1	197	8	0.01	12	0.01	68	0.01	6.6	49	0.01
KL34-09	676.7	679.7	1.03	10300	0.47	1.5	3000	1	2	7	0.01	119	0.01	5.3	28	0.01
KL34-09	679.7	682.7	2.76	27600	1.44	4.3	74400	6	1	7	1	347	0.01	33.0	35	0.01
KL34-09	682.7	685.7	1.74	17400	1.01	2.5	1330	1	1	6	0.01	145	0.01	5.0	19	0.01
KL34-09	685.7	688.7	2.46	24600	1.42	3.3	4800	8	0.01	58	0.01	155	0.01	15.0	27	0.01
KL34-09	688.7	691.7	3.95	39500	1.73	5.4	94600	10	2	24	0.01	231	0.01	35.0	53	0.01
KL34-09	691.7	693.3	1.8	18000	0.71	2.9	1600	6	1	22	0.01	124	0.01	18.0	76	0.01
KL34-09	693.3	695.4	0.8	8000	0.29	1.4	460	1	2	9	0.01	36	0.01	5.8	24	0.01
KL34-09	695.4	697.7	0.58	5800	0.25	1.7	205	7	8	16	0.01	18	0.01	4.8	49	0.01
KL34-09	697.7	700.7	0.4	4000	0.15	0.6	200	7	2	22	0.01	12	0.01	4.5	67	0.01
KL34-09	700.7	703.7	0.159	1590	0.05	0.6	111	7	2	41	0.01	9	0.01	2.0	82	0.01
KL34-09	703.7	706.3	0.2	2000	0.06	1.1	158	28	5	181	0.01	7	0.01	1.5	85	0.01
KL34-09	706.3	709.7	0.61	6100	0.2	1.8	150	10	2	38	0.01	16	0.01	6.5	54	0.01
KL34-09	709.7	712.7	0.4	4000	0.22	1.5	162	9	4	36	1	12	0.01	5.5	68	0.01
KL34-09	712.7	716.1	0.7	7000	0.35	2	94	7	3	11	1	10	0.01	5.0	56	0.01
KL34-09	716.1	718.7	0.59	5900	0.22	2.2	95	14	3	48	0.01	11	0.01	5.8	70	0.01
KL34-09	718.7	721.7	0.48	4800	0.23	2	171	30	4	83	1	11	0.3	5.4	74	0.01
KL34-09	721.7	724.7	0.436	4360	0.2	1.5	112	8	7	78	0.01	8	0.01	4.8	59	0.01
KL34-09	724.7	727.7	0.65	6500	0.21	1.6	96	14	4	80	0.01	12	0.01	4.9	129	0.01
KL34-09	727.7	730.7	0.447	4470	0.1	1.2	182	55	47	238	0.01	11	0.2	3.5	185	0.01
KL34-09	730.7	733.7	0.78	7800	0.29	1.9	103	9	3	59	0.01	9	0.01	5.2	102	0.01
KL34-09	733.7	736.7	0.6	6000	0.24	1.3	97	9	0.01	195	0.01	8	0.01	4.5	52	0.01
KL34-09	736.7	739.7	0.56	5600	0.25	1.5	107	12	2	158	0.01	11	0.01	4.5	92	0.01
KL34-09	739.7	742.7	0.72	7200	0.36	2.2	72	9	1	68	2	14	0.01	7.0	79	0.01
KL34-09	742.7	745.7	0.344	3440	0.16	1.2	81	12	1	67	0.01	9	0.01	3.8	38	0.01
KL34-09	745.7	748.7	0.428	4280	0.21	1.4	98	8	1	143	0.01	8	0.01	3.5	32	0.01
KL34-09	748.7	751.7	0.424	4240	0.19	1.2	86	10	1	108	0.01	10	0.01	2.5	54	0.01
KL34-09	751.7	754.7	0.431	4310	0.16	1	88	11	1	280	0.01	7	0.01	4.6	60	0.01
KL34-09	754.7	757.7	0.23	2300	0.1	0.7	72	14	2	258	0.01	8	0.01	4.0	59	0.01
KL34-09	757.7	760.7	0.2	2000	0.11	0.6	51	15	2	138	0.01	6	0.01	3.5	45	0.01
KL34-09	760.7	763.7	0.32	3200	0.13	0.6	77	14	1	225	0.01	6	0.01	3.3	58	0.01
KL34-09	763.7	766.7	0.23	2300	0.09	0.1	76	15	0.01	215	0.01	5	0.01	1.8	33	0.01
KL34-09	766.7	769.7	0.476	4760	0.2	0.9	84	13	1	495	0.01	7	0.01	4.8	25	0.01
KL34-09	769.7	772.7	0.31	3100	0.15	0.5	70	9	0.01	270	0.01	5	0.01	4.0	37	0.01
KL34-09	772.7	775.7	0.23	2300	0.13	0.1	71	10	2	345	0.01	6	0.01	3.8	44	0.01
KL34-09	775.7	778.7	0.28	2800	0.12	0.1	83	12	1	168	0.01	8	0.01	3.5	33	0.01
KL34-09	778.7	781.7	0.3	3000	0.18	0.1	113	12	0.01	110	0.01	8	0.01	3.3	54	0.01
KL34-09	781.7	784.7	0.4	4000	0.19	0.8	75	10	2	64	0.01	10	0.01	3.5	85	0.01
KL34-09	784.7	787.7	0.504	5040	0.26	1.2	80	9	1	70	0.01	14	0.01	5.7	78	0.01
KL34-09	787.7	790.7	0.41	4100	0.17	0.7	76	14	0.01	73	0.01	12	0.01	5.5	63	0.01
KL34-09	790.7	793.7	0.382	3820	0.2	0.6	61	6	0.01	63	0.01	11	0.01	3.0	59	0.01
KL34-09	793.7	796.7	0.387	3870	0.24	0.8	60	6	1	65	0.01	11	0.01	5.8	72	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL34-09	796.7	799.7	0.61	6100	0.25	1.5	45	10	1	41	0.01	13	0.01	5.2	122	0.01
KL34-09	799.7	802.7	0.331	3310	0.15	0.8	82	18	1	75	0.01	12	0.01	4.3	91	0.01
KL34-09	802.7	805.7	0.318	3180	0.14	0.7	80	8	1	93	0.01	9	0.01	4.3	82	0.01
KL34-09	805.7	808.7	0.3	3000	0.13	0.7	44	5	1	91	0.01	7	0.01	3.5	85	0.01
KL34-09	808.7	811.7	0.26	2600	0.13	0.6	45	7	1	65	0.01	9	0.01	3.8	72	0.01
KL34-09	811.7	814.7	0.197	1970	0.11	0.6	32	6	1	150	0.01	7	0.01	2.8	68	0.01
KL34-09	814.7	817.7	0.28	2800	0.12	0.9	38	6	0.01	302	0.01	5	0.01	4.0	91	0.01
KL34-09	817.7	820.7	0.24	2400	0.13	0.6	69	5	0.01	110	0.01	7	0.01	3.3	83	0.01
KL34-09	820.7	823.7	0.378	3780	0.23	0.8	52	6	1	100	0.01	8	0.01	5.1	68	0.01
KL34-09	823.7	826.7	0.27	2700	0.15	0.9	36	5	1	73	0.01	6	0.01	5.8	53	0.01
KL34-09	826.7	829.7	0.93	9300	0.36	2.2	65	8	0.01	122	0.01	10	0.01	6.8	48	0.01
KL34-09	829.7	832.1	0.58	5800	0.25	1.5	70	8	1	223	0.01	14	0.01	8.4	60	0.01
KL34-09	832.1	833.9	0.347	3470	0.13	0.9	39	10	1	253	0.01	12	0.01	6.8	41	0.01
KL34-09	833.9	835.7	0.427	4270	0.2	0.8	70	18	1	110	0.01	14	0.01	6.5	54	0.01
KL34-09	835.7	838.7	0.57	5700	0.26	1.2	62	10	2	120	0.01	13	0.01	7.3	81	0.01
KL34-09	838.7	841.7	0.329	3290	0.14	0.8	281	7	1	27	0.01	9	0.01	4.3	80	0.01
KL34-09	841.7	844.7	0.501	5010	0.28	0.9	51	7	1	42	0.01	13	0.01	6.9	38	0.01
KL34-09	844.7	847.7	0.57	5700	0.22	1.4	45	9	1	92	0.01	12	0.01	4.3	72	0.01
KL34-09	847.7	850.7	0.68	6800	0.27	1.4	42	6	2	34	0.01	10	0.01	3.3	76	0.01
KL34-09	850.7	853.7	0.502	5020	0.23	0.9	123	8	1	58	0.01	9	0.01	5.3	42	0.01
KL34-09	853.7	856.7	0.57	5700	0.22	1.2	49	13	2	60	0.01	11	0.6	6.3	47	0.1
KL34-09	856.7	859.7	0.517	5170	0.53	1.3	48	11	7	103	0.01	10	0.3	7.3	56	0.01
KL34-09	859.7	862.7	0.72	7200	0.27	1.8	41	8	2	63	0.01	11	0.4	5.8	89	0.01
KL34-09	862.7	865.7	0.411	4110	0.15	0.9	53	16	2	110	0.01	11	0.4	4.5	46	0.01
KL34-09	865.7	868.7	0.471	4710	0.21	1.4	50	12	2	135	0.01	12	0.2	6.5	67	0.01
KL34-09	868.7	871.7	0.407	4070	0.19	1	46	14	2	58	0.01	11	0.01	4.8	73	0.01
KL34-09	871.7	874.7	0.475	4750	0.23	1.5	41	10	1	54	0.01	11	0.01	5.5	52	0.01
KL34-09	874.7	877.7	0.347	3470	0.2	1	43	12	2	58	0.01	9	0.01	3.5	34	0.01
KL34-09	877.7	880.7	0.327	3270	0.18	1.1	36	8	1	95	0.01	9	0.01	5.5	57	0.01
KL34-09	880.7	883.7	0.513	5130	0.21	1.2	57	10	1	135	0.01	11	0.01	6.5	37	0.01
KL34-09	883.7	886.7	0.433	4330	0.23	1	48	7	0.01	145	0.01	12	0.01	6.3	45	0.01
KL34-09	886.7	889.7	0.523	5230	0.24	1.3	51	10	1	120	0.01	11	0.01	7.5	77	0.01
KL34-09	889.7	892.7	0.56	5600	0.22	1.8	270	124	1	110	1	10	0.01	5.8	76	0.01
KL34-09	892.7	895.7	1.01	10100	0.44	2.3	64	7	1	103	0.01	14	0.01	8.5	64	0.01
KL34-09	895.7	898.7	1.15	11500	0.49	2.8	40	7	1	70	0.01	13	0.01	9.5	80	0.01
KL34-09	898.7	901.7	0.79	7900	0.31	2	48	7	3	225	0.01	16	0.4	5.8	71	0.01
KL34-09	901.7	904.7	1.41	14100	0.55	3	68	8	1	185	0.01	24	0.01	8.5	61	0.01
KL34-09	904.7	907.7	0.54	5400	0.26	1.4	72	11	1	167	0.01	9	0.01	5.5	65	0.01
KL34-09	907.7	910.7	1.01	10100	0.41	2.4	80	14	21	165	2	14	1.4	6.8	59	0.01
KL34-09	910.7	913.7	0.77	7700	0.33	1.8	61	9	11	115	0.01	15	0.01	8.3	56	0.01
KL34-09	913.7	916.7	0.63	6300	0.32	1.5	143	102	17	124	0.01	11	0.7	6.0	80	0.01
KL34-09	916.7	919.7	0.9	9000	0.4	2.7	124	54	48	110	4	21	7	8.6	48	0.01
KL34-09	919.7	921.3	0.67	6700	0.27	1.7	71	24	13	260	0.01	12	1.7	4.0	72	0.01
KL34-09	921.3	922.4	0.64	6400	0.28	1.6	480	378	41	270	0.01	12	0.8	4.3	42	0.01
KL34-09	922.4	925	1.02	10200	0.43	1.9	84	31	12	363	0.01	13	0.8	8.0	70	0.01
KL34-09	925	928.4	0.3	3000	0.15	0.7	139	105	90	130	0.01	9	4.1	3.0	192	0.01
KL34-09	928.4	931.4	0.368	3680	0.17	0.9	34	15	40	80	0.01	6	0.3	3.2	98	0.01
KL34-09	931.4	934.4	0.328	3280	0.14	0.7	151	50	7	63	0.01	6	0.4	2.4	159	0.01
KL34-09	934.4	937.4	0.24	2400	0.11	0.1	251	100	36	105	0.01	4	0.7	1.8	167	0.01
KL34-09	937.4	940.4	0.21	2100	0.08	0.1	21	8	6	155	0.01	5	0.3	1.5	62	0.01
KL34-09	940.4	943.4	0.198	1980	0.09	0.1	21	6	3	148	0.01	3	0.3	1.5	53	0.01
KL34-09	943.4	946.4	0.23	2300	0.1	0.9	59	18	17	68	0.01	5	1.4	1.7	58	0.01
KL34-09	946.4	949.4	0.26	2600	0.07	1.7	156	47	23	94	0.01	2	0.6	2.7	50	0.01
KL34-09	949.4	952.4	0.33	3300	0.15	0.9	92	30	5	132	0.01	6	0.3	3.6	72	0.01
KL34-09	952.4	955.4	0.46	4600	0.24	1.4	62	75	160	90	0.01	5	1.4	2.5	63	0.01
KL34-09	955.4	958.4	0.24	2400	0.18	0.7	197	70	23	41	0.01	5	0.6	1.9	175	0.01
KL34-09	958.4	961.4	0.157	1570	0.05	0.1	142	46	7	29	0.01	2	0.3	1.4	98	0.01
KL34-09	961.4	964.4	0.38	3800	0.19	1	109	33	4	45	0.01	5	0.3	1.6	63	0.01
KL34-09	964.4	967.4	0.54	5400	0.3	1.4	40	13	6	32	0.01	7	0.8	2.8	188	0.01
KL34-09	967.4	970.4	0.69	6900	0.39	1.4	21	6	7	56	0.01	8	0.6	3.2	77	0.01
KL34-09	970.4	973.4	0.62	6200	0.37	1.5	49	12	20	53	0.01	11	1.2	3.5	78	0.01
KL34-09	973.4	975.9	0.69	6900	0.49	1.7	67	15	5	54	0.01	13	0.4	4.0	78	0.01
KL34-09	975.9	979	0.5	5000	0.32	1.2	36	27	6	17	0.01	8	0.4	2.6	96	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL34-09	979	982.2	0.53	5300	0.31	1.5	38	13	2	69	0.01	9	0.01	2.8	90	0.01
KL34-09	982.2	985.3	0.68	6800	0.48	1.6	20	8	0.01	64	0.01	10	0.01	2.8	184	0.01
KL34-09	985.3	988.4	0.51	5100	0.36	1.1	25	12	1	28	0.01	8	0.01	2.9	112	0.01
KL34-09	988.4	991.4	0.67	6700	0.52	1.4	79	24	1	67	0.01	11	0.01	3.4	197	0.01
KL34-09	991.4	994.4	0.54	5400	0.38	1.3	24	7	7	23	0.01	11	0.01	3.2	120	0.01
KL34-09	994.4	997.4	0.61	6100	0.45	1.2	28	51	410	26	0.01	10	7.7	3.6	67	0.01
KL34-09	997.4	1000.4	0.42	4200	0.25	1	30	15	15	49	0.01	5	0.2	1.8	163	0.01
KL34-09	1000.4	1003.4	0.45	4500	0.26	0.8	100	26	2	42	0.01	6	0.01	2.4	202	0.01
KL34-09	1003.4	1004.7	0.6	6000	0.34	1.3	82	29	5	46	0.01	8	0.2	2.7	190	0.01
KL34-09	1004.7	1007.8	0.53	5300	0.25	1.4	58	20	12	31	0.01	6	0.6	3.8	184	0.01
KL34-09	1007.8	1010.9	0.59	5900	0.31	1.3	125	15	2	34	0.01	8	0.01	3.2	105	0.01
KL34-09	1010.9	1014	0.5	5000	0.23	1.3	144	44	5	39	0.01	6	0.2	3.2	180	0.01
KL34-09	1014	1017.1	0.54	5400	0.36	1.2	60	16	1	39	0.01	9	0.01	3.4	96	0.01
KL34-09	1017.1	1020.2	0.49	4900	0.31	1.1	49	13	1	36	0.01	9	0.01	2.6	197	0.01
KL34-09	1020.2	1023.3	0.55	5500	0.35	1.1	62	14	3	50	0.01	9	0.7	3.8	86	0.01
KL34-09	1023.3	1026.4	0.65	6500	0.35	1.3	37	1	1	24	0.01	7	0.5	3.0	81	0.01
KL34-09	1026.4	1029.5	0.56	5600	0.31	1.2	23	6	1	60	0.01	7	0.01	3.0	72	0.01
KL34-09	1029.5	1032.6	0.47	4700	0.25	1	26	9	1	32	0.01	8	0.01	2.6	88	0.01
KL34-09	1032.6	1035.7	0.34	3400	0.17	1.1	35	9	3	65	0.01	10	0.4	3.0	166	0.01
KL34-09	1035.7	1038.8	0.56	5600	0.37	1.5	90	23	12	74	0.01	13	0.4	3.8	112	0.01
KL34-09	1038.8	1041.9	0.48	4800	0.24	1.1	25	12	1	75	0.01	13	0.01	3.0	92	0.01
KL34-09	1041.9	1045	0.54	5400	0.36	1.3	46	13	3	41	0.01	10	0.2	3.8	154	0.01
KL34-09	1045	1048.3	0.57	5700	0.38	1.3	27	12	2	65	0.01	11	0.3	4.8	150	0.01
KL34-09	1048.3	1051.4	0.63	6300	0.44	1.4	32	11	1	34	0.01	11	0.01	3.8	97	0.01
KL34-09	1051.4	1054.4	0.63	6300	0.47	1.3	30	10	1	70	0.01	9	0.2	2.6	106	0.01
KL34-09	1054.4	1057.4	0.48	4800	0.24	1.4	122	14	250	66	0.01	9	0.4	2.8	161	0.01
KL34-09	1057.4	1060.4	0.28	2800	0.19	0.7	85	15	14	67	0.01	5	0.6	1.8	83	0.01
KL34-09	1060.4	1063.4	0.178	1780	0.09	0.1	28	10	8	39	0.01	6	0.2	1.5	55	0.01
KL34-09	1063.4	1066.4	0.46	4600	0.35	0.9	23	9	3	43	0.01	5	0.01	2.0	97	0.01
KL34-09	1066.4	1069.4	0.49	4900	0.33	1.2	45	17	9	39	0.01	8	0.2	1.0	221	0.01
KL34-09	1069.4	1072.4	0.46	4600	0.41	1.5	41	21	6	42	0.01	6	0.01	1.0	78	0.01
KL34-09	1072.4	1075.4	0.41	4100	0.33	1.1	30	6	3	27	0.01	7	0.01	1.3	91	0.01
KL34-09	1075.4	1078.4	0.5	5000	0.65	1.4	39	16	42	33	0.01	9	3	1.6	168	0.01
KL34-09	1078.4	1081.4	0.57	5700	0.4	1.4	33	9	34	23	0.01	11	1.2	2.3	215	0.01
KL34-09	1081.4	1083	0.141	1410	0.2	0.6	102	31	3	15	0.01	12	0.01	2.4	77	0.01
KL34-09	1083	1085.6	0.3	3000	0.39	0.9	44	17	12	77	0.01	17	0.01	1.8	203	0.01
KL34-09	1085.6	1087.4	0.43	4300	0.5	1.3	30	12	0.01	25	0.01	10	0.01	1.5	207	0.01
KL34-09	1087.4	1090.4	0.33	3300	0.27	1.1	36	14	0.01	31	0.01	11	0.01	1.5	232	0.01
KL34-09	1090.4	1093.4	0.37	3700	0.33	1	47	18	120	69	0.01	11	2.9	1.7	226	0.01
KL34-09	1093.4	1096.4	0.46	4600	0.37	1.2	43	15	4	63	0.01	7	0.5	1.5	114	0.01
KL34-09	1096.4	1099.4	0.49	4900	0.37	1	34	10	5	30	0.01	10	0.01	1.5	96	0.01
KL34-09	1099.4	1102.4	0.57	5700	0.39	1.4	48	14	27	41	0.01	11	1.1	1.6	104	0.01
KL34-09	1102.4	1105.4	0.7	7000	0.52	1.4	46	14	150	50	0.01	13	8.3	4.5	91	0.01
KL34-09	1105.4	1107.7	0.5	5000	0.4	1.4	42	13	8	33	0.01	12	1	1.3	92	0.01
KL34-09	1107.7	1109.9	0.37	3700	0.23	1.1	45	11	3	43	0.01	13	0.2	2.6	59	0.01
KL34-09	1109.9	1111.4	0.34	3400	0.25	0.8	34	12	120	17	0.01	8	7.3	1.5	86	0.01
KL34-09	1111.4	1113.5	0.48	4800	0.31	0.8	57	18	200	26	0.01	10	11.3	1.8	78	0.01
KL34-09	1113.5	1116.7	0.35	3500	0.31	1.2	76	16	2	82	0.01	11	0.2	1.3	96	0.01
KL34-09	1116.7	1119.8	0.32	3200	0.26	1.4	50	13	0.01	20	0.01	10	0.2	1.1	98	0.01
KL34-09	1119.8	1121	0.58	5800	0.43	2.3	66	23	3	26	0.01	11	0.4	2.0	104	0.01
KL34-09	1121	1122.3	0.21	2100	0.24	1	59	16	0.01	38	0.01	12	0.4	1.1	53	0.01
KL34-09	1122.3	1125.4	0.145	1450	0.13	0.7	62	19	2	18	0.01	11	0.2	1.4	60	0.01
KL34-09	1125.4	1128.5	0.065	650	0.07	0.1	58	10	2	6	0.01	8	0.2	0.0	58	0.01
KL34-09	1128.5	1131.6	0.083	830	0.07	0.1	51	16	24	16	0.01	10	0.6	0.5	37	0.01
KL34-09	1131.6	1134.7	0.108	1080	0.13	0.6	55	17	2	9	0.01	9	0.2	0.0	55	0.01
KL34-09	1134.7	1137.4	0.086	860	0.09	0.1	57	15	2	11	0.01	8	0.2	0.0	47	0.01
KL34-09	1137.4	1140.9	0.163	1630	0.96	1	69	14	1	4	0.01	8	0.2	1.0	65	0.01
KL34-09	1140.9	1144	0.073	730	0.05	0.1	60	16	1	6	0.01	9	0.01	0.5	52	0.01
KL34-09	1144	1146.4	0.083	830	0.11	0.1	68	18	1	5	0.01	7	0.01	0.0	30	0.01
KL34-09	1146.4	1148.6	0.027	270	0.02	0.1	67	17	1	6	0.01	7	0.01	0.5	36	0.01
KL34-09	1148.6	1150.4	0.0296	296	0.03	0.1	73	18	2	6	0.01	6	0.01	0.0	35	0.01
KL34-09	1150.4	1153.4	0.014	140	0.01	0.1	66	12	2	8	0.01	8	0.01	0.0	34	0.01
KL34-09	1153.4	1156.4	0.0187	187	0.01	0.1	79	16	2	11	0.01	9	0.4	0.0	30	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL34-09	1156.4	1159.5	0.01		100	0.01	0.1	256	58	6	6	1	12	0.6	0.0	48	0.01
KL34-09	1159.5	1162.4	0.0197		197	0.01	0.1	56	16	1	7	0.01	9	0.01	0.0	24	0.01
KL34-09	1162.4	1165.4	0.0232		232	0.01	0.1	60	20	1	4	1	11	0.01	0.0	27	0.01
KL34-09	1165.4	1168.4	0.018		180	0.02	0.1	58	18	1	7	0.01	10	0.01	0.0	21	0.01
KL34-09	1168.4	1171.4	0.009		90	0.01	0.1	60	20	0.01	3	0.01	10	0.01	0.0	45	0.01
KL34-09	1171.4	1174.4	0.0164		164	0.03	0.1	53	34	2	8	0.01	11	0.3	0.0	23	0.01
KL34-09	1174.4	1177.4	0.0114		114	0.08	0.1	51	16	1	15	0.01	13	0.01	0.0	25	0.01
KL34-09	1177.4	1180.4	0.0159		159	0.01	0.1	42	20	1	11	0.01	12	0.01	0.0	54	0.01
KL34-09	1180.4	1183.4	0.0194		194	0.02	0.1	64	21	1	21	0.01	9	0.01	0.0	50	0.01
KL34-09	1183.4	1186.4	0.0152		152	0.01	0.1	58	16	0.01	8	0.01	8	0.01	0.0	28	0.01
KL34-09	1186.4	1189.4	0.0225		225	0.01	0.1	54	27	3	10	0.01	9	0.01	0.6	43	0.01
KL34-09	1189.4	1192.4	0.0131		131	0.01	0.1	48	17	0.01	2	0.01	8	0.01	0.0	24	0.01
KL34-09	1192.4	1195.4	0.0176		176	0.01	0.1	56	13	2	2	0.01	12	0.01	0.6	23	0.01
KL34-09	1195.4	1198.4	0.015		150	0.01	0.1	55	12	1	2	0.01	6	0.01	0.0	27	0.01
KL34-09	1198.4	1201.4	0.0053		53	0.01	0.1	53	14	1	2	0.01	6	0.01	0.0	48	0.01
KL34-09	1201.4	1204.4	0.068		680	0.12	0.1	54	13	1	10	0.01	13	0.01	0.6	26	0.01
KL34-09	1204.4	1207.4	0.0221		221	0.01	0.1	55	15	3	7	1	13	0.01	1.0	36	0.01
KL34-09	1207.4	1210.4	0.0104		104	0.01	0.1	44	6	0.01	7	0.01	9	0.01	0.0	48	0.01
KL34-09	1210.4	1213.4	0.0165		165	0.01	0.1	44	13	1	9	0.01	9	0.01	0.0	43	0.01
KL34-09	1213.4	1216.4	0.0226		226	0.01	0.1	43	7	1	7	0.01	10	0.01	0.0	29	0.01
KL34-09	1216.4	1219.4	0.0086		86	0.01	0.1	51	12	2	4	0.01	8	0.01	0.0	55	0.01
KL34-09	1219.4	1222.4	0.0114		114	0.01	0.1	36	10	1	2	0.01	8	0.01	0.0	37	0.01
KL34-09	1222.4	1225.4	0.183		1830	0.22	0.1	119	13	0.01	6	0.01	10	0.01	1.0	47	0.01
KL34-09	1225.4	1227	0.0129		129	0.01	0.1	40	8	2	9	0.01	12	0.01	0.0	43	0.01
KL34-09	1227	1229.4	0.0123		123	0.01	0.1	51	9	2	10	0.01	10	0.01	0.0	46	0.01
KL36-01	0	3	0.0011		11	0.03	0.1	237	101	3	8	0.01	1	1.2	2.3	19	0.01
KL36-01	3	6.7	0.0012		12	0.05	0.5	185	59	4	4	0.01	1	1.2	2.5	18	0.01
KL36-01	6.7	10.1	0.002		20	0.06	0.7	356	139	10	9	1	1	1.9	2.8	20	0.01
KL36-01	10.1	13.1	0.0057		57	0.1	0.6	310	76	7	4	0.01	1	2.2	2.0	21	0.01
KL36-01	13.1	16.1	0.001		10	0.1	0.8	410	183	4	3	0.01	1	2	2.8	35	0.01
KL36-01	16.1	19.1	0.0007		7	0.14	0.7	364	178	5	3	0.01	1	2	3.0	28	0.01
KL36-01	19.1	22.1	0.0005		5	0.23	1.1	610	268	8	3	0.01	1	2.4	2.8	38	0.1
KL36-01	22.1	25.1	0.0012		12	0.23	0.9	650	330	4	4	0.01	1	3	2.3	34	0.22
KL36-01	25.1	28.1	0.0007		7	0.26	0.9	490	176	4	2	0.01	1	3.1	2.3	55	0.1
KL36-01	28.1	31.1	0.0008		8	0.17	1.2	423	112	11	6	0.01	1	2.6	2.3	26	0.01
KL36-01	31.1	34.1	0.0007		7	0.1	1.1	311	122	19	10	0.01	1	2.3	2.0	23	0.01
KL36-01	34.1	37.1	0.0005		5	0.09	0.8	191	75	1	3	0.01	1	2.3	1.8	34	0.01
KL36-01	37.1	40.1	0.0011		11	0.34	1.5	910	275	18	4	0.01	1	3.7	2.9	24	0.2
KL36-01	40.1	43.1	0.0012		12	0.16	1	1240	214	30	7	0.01	1	5.5	1.8	33	0.1
KL36-01	43.1	46.1	0.0006		6	0.12	0.8	440	113	26	6	0.01	1	3.6	2.0	34	0.1
KL36-01	46.1	49.1	0.002		20	0.18	1.1	770	220	15	4	0.01	1	4.3	2.5	20	0.21
KL36-01	49.1	52.1	0.0005		5	0.21	1	910	183	9	2	0.01	1	2.3	3.0	22	0.24
KL36-01	52.1	55.1	0.0003		3	0.15	0.9	370	85	9	2	0.01	1	2	2.5	23	0.01
KL36-01	55.1	58.1	0.0008		8	0.11	0.7	141	48	8	3	0.01	1	1.7	2.0	27	0.01
KL36-01	58.1	61.1	0.0011		11	0.09	0.8	128	32	5	4	0.01	1	1.6	2.0	28	0.01
KL36-01	61.1	64.1	0.0014		14	0.19	0.7	226	51	9	3	0.01	1	2.9	2.0	29	0.01
KL36-01	64.1	67.1	0.0017		17	0.2	1.3	186	117	16	2	0.01	1	7.1	3.0	32	0.11
KL36-01	67.1	70.1	0.0053		53	0.29	1	174	53	10	5	0.01	1	3.4	9.0	47	0.1
KL36-01	70.1	73.1	0.0048		48	0.19	1.1	414	130	9	3	0.01	1	5.1	4.5	26	0.15
KL36-01	73.1	76.1	0.0307		307	0.62	7.5	13600	5700	43	8	0.01	1	16.6	98.0	81	0.41
KL36-01	76.1	79.1	0.05		500	0.18	20.1	16700	13000	98	6	1	1	39	192.0	72	1.09
KL36-01	79.1	82.1	0.0281		281	0.17	12.8	8000	7200	69	8	1	1	26	118.0	37	0.51
KL36-01	82.1	85.1	0.0012		12	0.08	0.6	247	112	9	3	0.01	1	4.2	2.8	36	0.01
KL36-01	88.1	91.1	0.0057		57	0.25	1.7	1280	620	29	9	0.01	1	18	3.8	24	0.24
KL36-01	91.1	94.1	0.0016		16	0.19	0.1	372	129	22	2	0.01	1	4	3.0	28	0.01
KL36-01	94.1	97.1	0.0052		52	0.38	4.3	1400	2450	94	3	9	3	18.5	43.2	44	0.1
KL36-01	97.1	100.1	0.003		30	0.36	1.5	2800	580	150	11	1	2	22	9.5	95	0.26
KL36-01	100.1	103.1	0.0167		167	0.43	2.8	4560	950	150	19	3	3	34	10.0	105	0.68
KL36-01	103.1	106.1	0.0067		67	0.39	6.5	5300	1620	88	15	5	3	20	8.3	103	0.46
KL36-01	106.1	107.9	0.0301		301	0.85	15.3	23500	8200	130	12	7	6	20	34.5	48	1.36
KL36-01	107.9	112.1	0.33		3300	1.28	28.5	16600	15200	1240	192	29	4	70	26.2	134	1.8
KL36-01	112.1	115.1	0.57		5700	1.01	6.5	3400	470	1890	180	32	1	134	13.3	151	1.6
KL36-01	115.1	118.1	0.0417		417	0.16	1.4	900	148	120	57	7	1	16.6	6.3	156	0.14

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL36-01	118.1	121.1	0.0305		305	0.09	3.8	1700	750	59	85	34	1	14.3	7.0	26	0.16
KL36-01	121.1	127.1	0.066		660	0.12	10.3	3550	2980	150	53	88	1	10.9	7.3	38	0.34
KL36-01	127.1	130.1	0.19		1900	0.09	7.7	890	395	400	347	46	1	22	6.5	37	0.19
KL36-01	130.1	133.1	0.0176		176	0.7	13.2	5900	3120	250	239	24	3	13.1	10.0	95	0.33
KL36-01	133.1	136.1	0.0183		183	0.73	13.4	6400	3100	290	169	22	1	12.6	9.5	103	0.35
KL36-01	136.1	139.1	0.0081		81	1.12	6.7	3880	1660	270	304	8	1	11.5	7.5	138	0.24
KL36-01	139.1	145.1	0.0091		91	0.96	5.4	6600	1810	260	686	6	3	10.6	12.8	200	0.23
KL36-01	145.1	148.1	0.0134		134	2.84	8.3	22900	1230	420	4410	670	9	18.8	64.0	117	0.7
KL36-01	148.1	151.1	0.017		170	1.53	5.1	7600	1470	310	1610	16	5	12.9	21.0	40	0.5
KL36-01	151.1	154.1	0.051		510	1.12	45	36300	17600	210	3180	71	5	17.8	70.0	299	1.3
KL36-01	154.1	157.1	0.044		440	0.71	19.5	9400	6000	46	77	14	1	22	44.0	33	0.5
KL36-01	157.1	160.1	0.0114		114	0.25	4.6	3310	1440	20	45	4	1	4.3	10.7	21	0.21
KL36-01	160.1	163.1	0.0058		58	0.11	2.5	1530	670	8	32	3	1	2.5	4.3	21	0.14
KL36-01	163.1	166.1	0.0059		59	0.14	5.3	1380	1710	7	28	9	1	8	14.9	25	0.19
KL36-01	166.1	169.1	0.0052		52	0.12	4.7	670	700	7	30	14	1	18.5	4.5	21	0.1
KL36-01	169.1	172.1	0.0056		56	0.3	3.2	1950	1230	15	42	3	1	11	7.3	25	0.4
KL36-01	172.1	175.1	0.0051		51	0.36	4.3	2050	730	11	124	6	1	16.8	5.5	32	0.61
KL36-01	175.1	178.1	0.051		510	1.61	29.2	15600	8700	150	80	12	2	60	42.0	27	1.8
KL36-01	178.1	181.1	0.0084		84	0.28	4	1610	670	39	81	4	1	16.2	5.8	33	0.42
KL36-01	181.1	184.2	0.0161		161	0.27	5.3	2090	1070	49	30	6	1	22	5.5	32	1.07
KL36-01	184.2	188.1	0.06		600	1.04	19.2	9700	7000	230	59	20	4	28	31.3	46	1.56
KL36-01	188.1	191.6	0.0194		194	2.3	7.5	3690	1910	140	90	8	3	16.3	16.8	36	0.98
KL36-01	191.6	194.6	0.058		580	2.22	17	8700	5600	190	1250	49	6	38	34.0	35	1.76
KL36-01	194.6	197.6	0.055		550	0.82	16.6	9100	2200	170	392	48	5	20	23.5	48	0.34
KL36-01	197.6	201.6	0.056		560	0.41	11.5	4300	1790	140	162	18	2	82	17.8	28	0.31
KL36-01	201.6	204.6	0.087		870	1.54	18.4	19400	1760	350	342	56	18	18	64.0	71	0.2
KL36-01	204.6	207.6	0.64		6400	2.97	34	50900	4100	660	1570	116	72	28	232.0	59	0.13
KL36-01	207.6	210.6	0.067		670	0.38	4.5	4700	2300	52	150	4	6	11.3	18.6	36	0.01
KL36-01	210.6	213.6	0.026		260	0.64	6.5	4900	1400	52	98	17	5	4.8	24.5	31	0.12
KL36-01	213.6	216.6	0.09		900	1.27	55	21800	36200	130	196	16	5	60	189.0	50	0.13
KL36-01	216.6	219.6	0.045		450	0.59	50	38500	32300	72	46	6	3	44	233.0	28	0.01
KL36-01	219.6	222.6	0.0299		299	0.32	31.1	17600	13900	40	66	4	2	22	142.0	25	0.01
KL36-01	222.6	229.6	0.099		990	1.03	56	17200	15700	200	283	15	5	34	134.0	91	0.64
KL36-01	229.6	232.6	0.0399		399	0.56	19.7	7300	2070	110	135	12	6	15.2	30.0	34	0.19
KL36-01	232.6	238	0.187		1870	0.42	13.6	7700	2200	320	205	26	9	20	27.0	30	0.17
KL36-01	238	241.9	0.0064		64	0.32	2	590	318	24	20	1	3	3.3	7.0	24	0.01
KL36-01	241.9	244.7	0.0037		37	0.65	1.8	345	175	42	16	0.01	4	6.2	7.3	28	0.1
KL36-01	244.7	247.2	0.0027		27	0.05	0.1	140	93	17	5	0.01	2	1.2	2.8	12	0.01
KL36-01	247.2	251.4	0.003		30	0.04	0.9	312	87	27	63	1	2	1.5	5.3	19	0.01
KL36-01	251.4	254.4	0.0024		24	0.09	0.6	124	53	10	7	0.01	1	1	3.8	13	0.01
KL36-01	254.4	264.2	0.0042		42	0.23	1.7	1120	540	20	9	3	1	4	8.8	20	0.01
KL36-01	264.2	268.9	0.0054		54	0.2	1.7	690	334	30	16	3	2	3.9	25.0	25	0.1
KL36-01	268.9	270.6	0.002		20	0.01	0.1	281	187	3	6	0.01	1	0.8	2.3	15	0.01
KL36-01	270.6	273	0.0041		41	0.07	0.8	710	101	14	15	3	2	1	4.5	15	0.01
KL36-01	273	275.2	0.0019		19	0.03	1	540	1150	11	3	0.01	1	1.6	4.8	17	0.01
KL36-01	275.2	278.9	0.005		50	0.11	1.7	780	500	15	9	2	1	2.6	8.8	22	0.01
KL36-01	278.9	281.4	0.002		20	0.33	1.3	243	181	24	10	1	1	4.1	5.7	33	0.01
KL36-01	281.4	287.4	0.002		20	0.16	1.1	201	148	9	5	1	1	1.3	3.0	20	0.01
KL36-01	287.4	292.2	0.0026		26	0.12	1	368	185	16	4	1	1	1.5	4.6	25	0.01
KL36-01	292.2	295.6	0.001		10	0.04	0.1	200	127	7	1	0.01	1	0.5	1.5	16	0.01
KL36-01	295.6	299.3	0.0011		11	0.15	0.7	228	219	18	2	0.01	1	1	3.5	21	0.01
KL36-01	299.3	302.4	0.0048		48	0.06	1.3	4750	557	10	3	2	1	1.6	9.3	22	0.01
KL36-01	302.4	306.4	0.053		530	0.06	1.4	1130	414	14	4	1	1	1.4	5.5	25	0.01
KL36-01	306.4	310.8	0.0016		16	0.03	0.7	81	173	7	3	1	1	0.4	4.4	20	0.01
KL36-01	310.8	314.4	0.0015		15	0.01	0.1	97	98	7	4	0.01	1	0.4	3.0	26	0.01
KL36-01	314.4	317.4	0.0015		15	0.03	0.1	233	214	8	3	0.01	1	0.5	5.5	23	0.01
KL36-01	317.4	320.4	0.003		30	0.06	0.1	277	270	10	3	0.01	1	0.9	5.0	27	0.01
KL36-01	320.4	325.2	0.0024		24	0.04	0.1	278	311	9	4	0.01	1	0.9	7.3	22	0.01
KL36-01	325.2	328.2	0.0013		13	0.04	1.5	1600	1020	7	3	0.01	1	2.6	4.0	21	0.01
KL36-01	328.2	331.3	0.0025		25	0.05	0.6	281	270	8	4	1	1	0.6	5.8	24	0.01
KL36-01	331.3	334.1	0.0064		64	0.03	0.5	600	200	9	8	0.01	1	0.7	3.8	19	0.01
KL36-01	334.1	336.3	0.0073		73	0.02	0.1	289	132	6	13	0.01	1	1	2.6	16	0.01
KL36-01	336.3	340.3	0.0074		74	0.03	0.1	217	165	10	10	0.01	1	0.6	4.0	17	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL36-01	340.3	343.3	0.0077		77	0.01	0.1	96	55	12	9	0.01	1	0.8	1.1	22	0.01
KL36-01	343.3	346.6	0.0124		124	0.02	0.1	380	94	13	14	0.01	1	1.4	2.3	18	0.01
KL36-01	346.6	350.4	0.0054		54	0.02	0.1	396	333	7	6	0.01	1	0.8	3.5	20	0.01
KL36-01	350.4	353.2	0.0062		62	0.05	0.1	167	167	13	6	0.01	1	1.7	6.3	20	0.01
KL36-01	353.2	355.9	0.0055		55	0.07	0.1	680	384	9	2	0.01	1	2.1	3.5	23	0.01
KL36-01	355.9	359.4	0.0059		59	0.11	0.1	280	194	10	3	0.01	1	1	5.0	25	0.01
KL36-01	359.4	362.4	0.0156		156	0.16	3.6	3200	2100	26	4	1	1	5.2	26.8	35	0.01
KL36-01	362.4	365.4	0.0261		261	0.19	13.5	9400	6900	71	5	0.01	1	17.2	30.5	25	0.12
KL36-01	365.4	368.4	0.0125		125	0.09	0.7	428	277	17	5	0.01	1	1.4	4.8	26	0.01
KL36-01	368.4	371.4	0.051		510	0.08	2.1	960	520	120	7	1	1	6.5	5.8	29	0.01
KL36-02	0	4	0.0077		77	0.01	0.1	129	57	8	6	0.01	1	0.5	1.9	20	0.01
KL36-02	4	8.5	0.0026		26	0.01	0.1	101	44	5	6	1	1	0.5	2.8	19	0.01
KL36-02	8.5	11.5	0.0024		24	0.01	0.1	180	65	6	4	1	1	0.6	2.5	23	0.01
KL36-02	11.5	14.5	0.0018		18	0.04	0.5	280	95	10	3	0.01	1	1	3.0	18	0.01
KL36-02	14.5	17.2	0.0047		47	0.02	0.5	284	116	11	4	0.01	1	1.1	1.7	20	0.01
KL36-02	17.2	20.5	0.0025		25	0.06	1.6	930	460	23	2	0.01	1	4.7	1.3	22	0.01
KL36-02	20.5	23.5	0.0043		43	0.12	2.4	1450	650	39	5	0.01	2	4.7	2.0	30	0.01
KL36-02	23.5	26.5	0.0019		19	0.07	1.3	820	368	13	3	0.01	1	2.3	2.4	29	0.01
KL36-02	26.5	29.5	0.0029		29	0.06	1	640	296	13	5	0.01	1	2.7	3.3	16	0.01
KL36-02	29.5	32.5	0.0027		27	0.19	2.9	1560	600	27	5	0.01	1	4.8	3.8	22	0.13
KL36-02	32.5	35.5	0.0026		26	0.11	1.3	640	270	16	4	0.01	1	2.1	3.0	23	0.01
KL36-02	35.5	38.5	0.0093		93	0.08	0.8	304	88	12	3	0.01	1	1.8	3.7	21	0.01
KL36-02	38.5	41.5	0.0022		22	0.08	1.1	470	234	24	8	1	1	2.8	3.3	22	0.01
KL36-02	41.5	44.5	0.0108		108	0.04	1.4	660	221	16	7	0.01	1	2.1	3.5	24	0.01
KL36-02	44.5	47.5	0.0033		33	0.02	0.1	97	53	16	6	1	1	1	4.0	20	0.01
KL36-02	47.5	50.5	0.0066		66	0.04	0.7	440	265	29	5	1	1	4.1	5.3	29	0.01
KL36-02	50.5	53.5	0.0045		45	0.38	2.2	2100	3000	110	3	0.01	1	4.2	8.3	26	0.76
KL36-02	53.5	56.5	0.0049		49	0.09	1.5	1960	1320	18	4	0.01	1	3.5	9.0	20	0.21
KL36-02	56.5	59.5	0.0123		123	0.16	0.1	312	127	29	7	0.01	3	2.2	3.0	28	0.01
KL36-02	59.5	62.5	0.0074		74	0.1	0.5	540	192	35	6	0.01	2	3	4.0	33	0.01
KL36-02	62.5	65.5	0.0029		29	0.04	0.1	189	67	15	3	0.01	1	1	2.9	32	0.29
KL36-02	65.5	68.5	0.0043		43	0.03	0.1	200	146	21	4	0.01	1	1.6	4.8	24	0.01
KL36-02	68.5	71.5	0.0162		162	0.13	1.4	1190	330	80	9	15	4	6.3	5.3	68	0.25
KL36-02	71.5	74.5	0.0166		166	0.05	4	6100	2300	35	10	12	4	2.7	21.9	41	0.16
KL36-02	74.5	76.3	0.0349		349	0.03	2.1	1080	780	90	8	5	1	6.2	8.0	15	0.01
KL36-02	76.3	80.5	0.61		6100	0.18	32	3600	7100	180	126	421	8	20.5	20.6	57	0.1
KL36-02	80.5	83.5	1		10000	0.39	60	7850	39700	1130	550	105	4	50	113.5	162	0.53
KL36-02	83.5	86.5	0.0161		161	0.32	7.5	2730	1500	83	53	37	4	4.5	4.5	180	0.16
KL36-02	86.5	89.5	0.0084		84	0.39	2.1	3400	780	150	119	3	5	16.7	4.3	177	0.38
KL36-02	89.5	92.5	0.0182		182	0.25	4.5	2620	886	43	144	23	3	10.2	8.0	165	0.32
KL36-02	92.5	95.5	0.0257		257	0.1	1.4	1280	314	100	41	3	1	5.4	1.5	59	0.11
KL36-02	95.5	99.9	0.0159		159	0.06	0.5	388	102	30	40	0.01	1	3.1	5.3	31	0.01
KL36-02	99.9	104.5	0.0142		142	0.02	0.5	318	177	37	263	0.01	1	3.1	2.5	28	0.01
KL36-02	104.5	107.5	0.0079		79	0.44	4.7	9100	1660	110	100	2	1	14	8.3	36	1.04
KL36-02	107.5	111	0.0117		117	0.44	3.7	5300	1150	140	95	5	2	13.5	4.5	47	0.35
KL36-02	111	113.5	0.0115		115	0.09	4.3	1400	2030	31	23	9	1	7.2	7.5	24	0.11
KL36-02	113.5	116.5	0.0384		384	0.12	2.3	5700	1980	37	42	2	1	12.2	8.5	19	0.1
KL36-02	116.5	119.5	0.0143		143	0.06	1.4	910	289	31	25	8	1	3	1.4	23	0.01
KL36-02	119.5	122.5	0.0171		171	0.05	0.9	440	226	18	18	4	1	2.1	3.2	24	0.01
KL36-02	122.5	125.5	0.0086		86	0.01	0.8	760	390	13	20	2	1	1.1	2.4	25	0.01
KL36-02	125.5	128.5	0.0187		187	0.01	0.7	520	268	19	18	3	1	1.9	3.0	26	0.01
KL36-02	128.5	131.5	0.0106		106	0.01	0.9	770	368	10	32	2	1	1.3	3.5	25	0.01
KL36-02	131.5	134.5	0.0036		36	0.01	0.1	408	65	8	25	2	1	0.4	1.7	28	0.01
KL36-02	134.5	137.5	0.0283		283	0.05	1.4	2830	193	50	17	7	3	3.8	5.8	24	0.01
KL36-02	137.5	140.5	0.102		1020	0.71	7	5330	1220	150	245	78	15	46	18.0	36	0.1
KL36-02	140.5	143.5	0.0307		307	0.08	2.5	4630	497	59	34	10	3	34	7.3	31	0.01
KL36-02	143.5	146.5	0.0096		96	0.07	1.1	1120	340	38	325	3	2	12	5.5	24	0.01
KL36-02	146.5	150	0.0034		34	0.05	1	980	420	13	30	0.01	1	1.7	9.8	14	0.01
KL36-02	150	152.5	0.0104		104	0.08	5.4	5070	1470	42	20	8	7	4.8	9.4	19	0.01
KL36-02	152.5	155.5	0.0076		76	0.06	1.5	1190	720	22	13	3	1	1.8	4.3	12	0.01
KL36-02	155.5	158.5	0.0141		141	0.06	1.1	1800	750	31	16	1	1	2.6	2.3	16	0.01
KL36-02	158.5	161.5	0.058		580	0.12	3.3	7100	1100	140	43	19	8	9.8	6.0	19	0.1
KL36-02	161.5	164.5	0.023		230	0.2	8.6	12200	8000	61	46	7	4	14.4	11.8	25	0.16

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL36-02	164.5	167.5	0.0281		281	0.17	12.1	2300	4800	81	131	24	3	7.5	27.0	18	0.12
KL36-02	167.5	170.5	0.0187		187	0.21	4.3	5400	4400	35	49	5	1	6.2	9.8	19	0.42
KL36-02	170.5	173.5	0.031		310	0.31	5	6500	2400	70	67	6	2	7.4	9.8	21	1.3
KL36-02	173.5	176.5	0.0227		227	0.19	3.7	4430	1980	47	35	5	1	4.3	9.0	27	1.23
KL36-02	176.5	179.5	0.0393		393	0.17	4.2	6400	4300	59	39	4	4	6.6	11.3	21	0.53
KL36-02	179.5	182.5	0.0369		369	0.45	5.4	4560	3080	110	130	10	3	4.5	12.1	27	1.84
KL36-02	182.5	185.5	0.0277		277	0.17	3.1	3740	1590	65	28	6	1	3.7	10.3	14	0.72
KL36-02	185.5	188.5	0.0381		381	0.47	21.5	5700	10400	150	27	47	2	6.1	24.5	47	0.82
KL36-02	188.5	192.5	0.0344		344	0.41	11.3	18900	1780	150	33	61	2	1.3	30.2	50	0.53
KL36-02	192.5	194.5	0.0285		285	0.4	3	2070	1130	140	22	7	4	3	8.8	46	0.36
KL36-02	194.5	197.5	0.103		1030	1.53	41	28900	30400	230	33	132	6	17.5	75.8	63	1.7
KL36-02	197.5	203.5	0.9		9000	1.82	3.2	670	289	140	20	52	16	3.1	27.0	115	0.19
KL36-02	203.5	206.5	0.97		9700	1.43	5	2600	365	36	10	76	30	2.7	64.3	189	0.11
KL36-02	206.5	209.5	1.39		13900	2.44	8	3000	1260	1320	64	70	53	9.4	41.0	318	2.35
KL36-02	209.5	212.5	1.02		10200	1.07	8.8	750	430	1960	84	38	40	22	24.5	321	1
KL36-02	212.5	215	1.67		16700	0.44	8	940	239	1710	2150	26	48	25	30.5	374	0.96
KL36-02	215	221.5	2.16		21600	0.62	12	690	3300	2400	498	13	41	24	45.0	269	1.23
KL36-02	221.5	227.5	5.72		57200	0.78	39	1760	970	3800	26	36	66	26	37.5	88	1.86
KL36-02	227.5	232.5	0.72		7200	1.17	8.5	1140	1210	1020	102	7	103	9.3	67.0	85	0.33
KL36-02	232.5	236	3.06		30600	0.71	13.6	1130	800	580	105	2	53	12.7	40.5	159	0.55
KL36-02	236	239.5	0.34		3400	0.55	4.5	410	2900	230	221	3	66	7.8	38.0	192	0.19
KL36-02	239.5	242.5	2.3		23000	0.78	7.4	184	570	220	63	1	73	7.6	45.0	71	0.32
KL36-02	242.5	248.5	1.67		16700	0.52	4.7	80	81	180	44	2	51	3.7	33.5	146	0.31
KL36-02	248.5	251.5	2.63		26300	0.64	4.3	153	51	710	32	1	68	22	35.0	75	0.96
KL36-02	251.5	254.5	4.2		42000	0.95	6.9	63	34	260	69	2	82	7	46.0	96	0.46
KL36-02	254.5	257.5	2.14		21400	1.05	3.8	119	44	180	18	2	85	5.3	84.0	74	0.24
KL36-02	257.5	259.5	1.42		14200	0.96	5.8	227	63	300	81	13	86	3.4	87.5	117	0.01
KL36-02	259.5	262.5	2.03		20300	0.95	10.3	240	64	310	33	7	192	4.9	140.0	59	0.01
KL36-02	262.5	266.5	2.24		22400	0.77	3.2	86	58	260	105	3	109	1.1	46.0	105	0.01
KL36-02	266.5	269.5	2.26		22600	0.88	2.9	69	59	130	98	3	107	0.7	48.0	123	0.01
KL36-02	269.5	272.5	1.87		18700	0.68	4.6	199	392	340	127	5	92	6.7	50.0	125	0.01
KL36-02	272.5	274	2.84		28400	1.12	4.4	166	223	160	63	4	97	2.3	38.0	86	0.01
KL36-02	274	277	2.66		26600	0.82	2.9	253	189	160	70	3	69	0.7	35.0	92	0.01
KL36-02	277	280	1.12		11200	0.68	3.5	700	640	270	76	5	76	1.4	42.7	313	0.11
KL36-02	280	283	1.24		12400	0.8	2.4	223	99	290	40	5	50	1.3	27.3	94	0.15
KL36-02	283	285.5	1.04		10400	0.56	3.2	153	98	480	38	9	32	2.8	30.0	305	0.13
KL36-02	285.5	289.5	1.25		12500	0.6	3	163	116	46	47	5	55	0.8	29.0	138	0.11
KL36-02	289.5	291.9	0.75		7500	1.73	2.1	116	119	210	15	18	50	1.7	66.5	35	0.1
KL36-02	291.9	294.5	1.67		16700	2.43	6.3	690	299	1280	47	68	19	5	50.0	158	0.11
KL36-02	294.5	298	1.12		11200	1.39	7.8	940	211	42	19	108	14	2.3	25.3	101	0.01
KL36-02	298	300.5	0.41		4100	1.52	8.3	1320	354	53	5	540	5	2.9	12.8	159	0.01
KL36-02	300.5	302.5	0.61		6100	1.26	8.9	1460	820	130	9	273	4	3	16.3	133	0.01
KL36-02	302.5	304.5	0.51		5100	1.37	6.2	53600	332	64	82	110	5	3.6	12.8	171	0.15
KL36-02	304.5	308	1.59		15900	2.33	20.2	141000	304	250	50	230	6	3	30.5	277	0.15
KL36-02	308	311	14.9		149000	1.66	77	1190	356	410	5	880	1	46	3.0	85	0.01
KL36-02	311	317.5	1.81		18100	0.9	7.7	1130	275	530	10	41	5	4.6	38.0	115	0.01
KL36-02	317.5	320.5	0.65		6500	0.78	3	690	202	520	55	19	12	2.8	54.0	42	0.01
KL36-02	320.5	323.5	0.8		8000	0.92	4.3	1300	560	610	1120	23	63	3.5	110.0	154	0.01
KL36-02	323.5	328.5	0.26		2600	6.34	16.1	17500	3700	840	18	107	5	12.8	53.2	100	0.5
KL36-02	328.5	331.5	0.33		3300	1.88	6.4	4800	660	630	11	67	14	4.3	59.0	110	0.12
KL36-02	331.5	334.5	0.94		9400	1.94	2.6	259	73	200	64	37	22	2.4	91.0	89	0.1
KL36-02	334.5	337.6	1.23		12300	2.1	3.9	269	116	840	13	67	9	1.3	100.0	90	0.01
KL36-02	337.6	340.5	0.38		3800	0.86	3.7	261	171	960	33	157	6	1.6	85.0	95	0.01
KL36-02	340.5	342.5	0.6		6000	1.72	4.8	266	194	790	9	172	26	0.9	44.0	120	0.01
KL36-02	342.5	345.5	2.17		21700	4.82	9.2	1160	138	2700	15	159	9	2.1	53.0	135	0.1
KL36-02	345.5	348.5	0.74		7400	3.48	7.6	23000	190	160	49	155	18	4.6	33.0	110	0.01
KL36-02	348.5	350	0.56		5600	2.12	8.1	24300	380	130	75	221	13	3.5	63.0	87	0.01
KL36-02	350	353	0.45		4500	2.84	2.4	710	165	140	42	31	11	3.6	68.3	148	0.01
KL36-02	353	354.8	0.31		3100	2.66	4.5	4700	132	210	63	70	9	12.9	64.8	107	0.01
KL36-02	354.8	356.5	0.33		3300	2.52	4.2	7200	178	250	88	141	8	10.8	65.0	110	0.01
KL36-02	356.5	359.5	0.0291		291	7.61	1.5	1730	98	200	87	44	6	22	6.6	96	0.01
KL36-02	359.5	362.5	0.0095		95	1.1	0.1	257	43	53	11	3	3	9.2	11.0	44	0.01
KL36-02	362.5	365.5	0.0189		189	0.77	0.7	5200	180	170	24	2	14	20	9.3	52	0.1

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL36-02	365.5	368.5	0.0113	113	0.96	3.1	1250	920	150	14	7	6	22	28.8	81	0.1
KL36-02	368.5	371.5	1.31	13100	1.88	38	25500	20500	630	31	38	4	32	29.0	162	0.14
KL36-02	371.5	374.5	0.115	1150	3.28	86	27000	22500	870	77	148	7	66	155.5	236	0.44
KL36-02	374.5	376.5	0.107	1070	4.52	6.3	6000	1180	620	44	83	7	20	16.0	207	0.1
KL36-02	376.5	379.5	0.278	2780	4.74	3.2	484	450	600	36	176	4	5.5	30.2	179	0.01
KL36-02	379.5	384.5	1.25	12500	2.08	4	368	256	1680	36	26	45	2.4	56.0	191	0.01
KL36-02	384.5	386.5	1.36	13600	2.16	4.1	520	275	790	60	22	21	3	46.5	192	0.01
KL36-02	386.5	389	1	10000	2.12	3	388	169	450	19	9	14	2.2	37.9	189	0.01
KL36-02	389	392	1.35	13500	2.58	3.5	890	218	2650	17	8	34	2.3	36.0	231	0.11
KL36-02	392	394.5	0.55	5500	1.38	1.9	450	151	1100	60	3	45	3.6	32.4	234	0.01
KL36-02	394.5	396.5	1.27	12700	2.62	3.8	1080	420	1890	20	3	58	3.3	21.5	192	0.01
KL36-02	396.5	399.5	1.25	12500	2.48	4.5	3800	1050	310	50	12	62	2.5	32.7	148	0.01
KL36-02	399.5	401.5	0.53	5300	1.22	2.7	1660	460	46	232	13	13	1.9	10.3	108	0.01
KL36-02	401.5	404.5	0.75	7500	1.18	4.7	1370	600	59	670	5	10	3.8	9.5	66	0.01
KL36-02	404.5	407.5	0.7	7000	1.16	3.1	289	268	56	112	5	15	2.8	12.3	81	0.01
KL36-02	407.5	409.5	0.58	5800	1.26	4.3	990	970	240	1020	6	23	4.2	12.8	91	0.01
KL36-02	409.5	412.5	0.313	3130	0.86	3.7	810	1070	65	134	3	16	2.6	11.3	104	0.01
KL36-02	412.5	415	0.148	1480	0.29	2.4	1180	480	120	750	12	8	1.8	11.8	90	0.01
KL36-02	415	418	0.145	1450	0.23	4.4	1460	960	150	165	15	11	4	11.8	185	0.01
KL36-02	418	421	0.349	3490	0.29	6.2	2260	1070	150	692	43	9	6.8	15.8	99	0.01
KL36-02	421	423.5	0.059	590	0.11	2.1	460	267	27	261	5	7	1.1	12.0	76	0.01
KL36-02	423.5	425.5	0.101	1010	0.17	2.3	670	280	30	224	7	9	1.2	14.0	70	0.01
KL36-02	425.5	427.5	0.046	460	0.15	1.7	224	196	23	299	4	5	0.7	5.0	49	0.01
KL36-02	427.5	430.4	0.203	2030	0.14	3.1	320	190	38	524	11	9	0.9	7.3	69	0.01
KL36-02	430.4	433.4	0.467	4670	0.18	6.5	510	187	370	273	34	10	1.7	8.1	113	0.01
KL36-02	433.4	436	0.327	3270	0.22	12.2	5380	4020	670	79	16	12	8.2	9.5	105	0.01
KL36-02	436	438.6	0.383	3830	0.2	9.6	4300	2800	820	55	14	8	9.6	5.8	91	0.01
KL36-02	438.6	440.7	0.41	4100	0.68	9.2	5300	2510	220	960	10	10	10.4	12.3	93	0.01
KL36-02	440.7	443.5	0.58	5800	1.07	10.6	4140	1410	180	404	10	8	9.6	11.8	51	0.01
KL36-02	443.5	446.5	0.305	3050	0.74	6.3	2410	310	140	740	17	6	4.9	7.5	55	0.01
KL36-02	446.5	449.5	0.342	3420	0.96	5.5	2150	440	230	500	6	8	10.4	7.6	98	0.01
KL36-02	449.5	452.5	0.51	5100	2.33	9.8	3480	730	380	560	9	9	17.6	10.1	121	0.01
KL36-02	452.5	455.5	0.367	3670	2.22	7.2	4640	1780	360	755	3	10	15	9.5	89	0.01
KL36-02	455.5	458.2	0.316	3160	1.44	6.4	4540	1550	500	1000	3	10	11.7	8.5	112	0.01
KL36-02	458.2	461.3	0.88	8800	2.24	9.6	1050	1330	400	415	2	14	15.6	18.0	85	0.01
KL36-02	461.3	463.5	0.206	2060	1.61	2.2	260	410	240	896	7	7	9.7	13.3	88	0.01
KL36-02	463.5	466	0.32	3200	1.18	3.1	360	470	300	600	7	9	7.3	9.8	136	0.01
KL36-02	466	469	0.358	3580	1.45	2.7	460	364	310	1640	9	10	11.6	9.8	127	0.01
KL36-02	469	473.5	0.168	1680	1.28	1.8	430	357	220	930	30	8	6.5	7.8	118	0.01
KL36-03	0	3.6	0.0068	68	0.01	0.8	210	76	11	4	0.01	1	1.3	1.8	20	0.01
KL36-03	3.6	5.7	0.0086	86	0.01	0.6	199	135	11	3	0.01	1	1	1.0	24	0.01
KL36-03	5.7	8.7	0.0094	94	0.03	0.7	490	192	10	7	0.01	1	1.6	1.4	22	0.01
KL36-03	8.7	10.8	0.0078	78	0.09	3.8	1920	1410	23	10	0.01	1	6.7	2.0	25	0.01
KL36-03	10.8	13.2	0.0052	52	0.03	1.1	364	263	14	5	0.01	1	1.3	1.6	23	0.01
KL36-03	13.2	16	0.0056	56	0.04	0.8	366	192	10	4	0.01	1	2.1	1.3	21	0.01
KL36-03	16	17.7	0.0146	146	0.02	0.7	310	158	12	8	0.01	1	1.5	1.3	26	0.01
KL36-03	17.7	20.7	0.0111	111	0.04	1.5	1000	400	15	6	0.01	1	3.1	1.8	27	0.01
KL36-03	20.7	23.5	0.014	140	0.07	1.9	1530	590	14	4	0.01	2	3.3	1.1	24	0.01
KL36-03	23.5	26.7	0.0271	271	0.21	11.4	8300	4900	63	39	7	2	16.6	6.0	25	0.28
KL36-03	26.7	29.7	0.0102	102	0.07	1.7	1120	690	18	7	0.01	1	2.9	2.0	22	0.1
KL36-03	29.7	32.2	0.0142	142	0.05	1.1	830	357	17	6	0.01	1	2.2	1.5	20	0.01
KL36-03	32.2	35.5	0.0083	83	0.02	0.5	340	121	10	8	0.01	1	1.2	1.5	23	0.01
KL36-03	35.5	38.6	0.006	60	0.03	0.9	416	309	16	4	0.01	1	1.4	1.0	22	0.01
KL36-03	38.6	41.6	0.0099	99	0.01	0.7	259	120	13	4	0.01	1	1.5	1.2	22	0.01
KL36-03	41.6	44.7	0.0048	48	0.02	0.9	490	220	20	8	1	1	2.2	1.5	22	0.01
KL36-03	44.7	47.7	0.006	60	0.01	0.5	191	110	14	3	0.01	1	1.3	1.3	22	0.01
KL36-03	47.7	50.7	0.0106	106	0.02	1.2	650	670	35	3	1	1	7	3.3	25	0.01
KL36-03	50.7	53.7	0.0117	117	0.05	0.7	1030	690	36	4	0.01	1	13.5	2.0	24	0.24
KL36-03	53.7	56.7	0.0056	56	0.03	0.7	171	255	24	3	0.01	1	2	2.0	20	0.01
KL36-03	56.7	59.7	0.0087	87	0.04	1	540	520	39	3	1	1	6	3.8	24	0.01
KL36-03	59.7	62.7	0.0068	68	0.14	1.2	1730	780	130	5	0.01	1	17.3	4.8	26	0.53
KL36-03	62.7	65.7	0.006	60	0.07	0.8	450	430	28	4	0.01	1	2.7	2.0	31	0.01
KL36-03	65.7	68.7	0.0069	69	0.06	0.1	570	394	22	5	0.01	1	6	2.1	35	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL36-03	68.7	71.7	0.0308		308	0.17	1.4	620	309	130	43	23	1	5.4	4.8	54	0.01
KL36-03	71.7	74.7	0.052		520	0.37	3.2	4600	1680	190	400	10	4	12.5	7.5	51	0.01
KL36-03	74.7	77.2	0.0263		263	0.12	0.8	1260	430	140	8	2	1	11.2	3.8	50	0.36
KL36-03	77.2	80.2	0.0345		345	0.14	3.5	490	430	57	14	96	4	3.2	13.0	36	0.01
KL36-03	80.2	81.3	0.051		510	0.07	5.1	640	490	63	33	126	5	3.5	5.5	43	0.01
KL36-03	81.3	83.7	0.177		1770	0.28	7.4	4200	3800	310	350	26	3	13.3	10.0	55	0.01
KL36-03	83.7	86.7	0.0283		283	0.33	4.4	2100	1310	140	73	17	2	7.6	10.5	38	0.17
KL36-03	86.7	89.7	0.0397		397	0.27	2.2	1580	880	170	124	5	1	13.3	6.0	42	0.01
KL36-03	89.7	91.9	0.0214		214	0.23	1.1	189	84	110	171	13	1	8.4	4.3	54	0.01
KL36-03	91.9	93.8	0.043		430	0.21	3.5	3300	1350	150	340	15	2	9.9	7.5	40	0.01
KL36-03	93.8	95.7	0.104		1040	0.08	2.1	1070	460	240	53	12	1	12.2	3.2	35	0.01
KL36-03	95.7	97.8	0.0162		162	0.05	1.3	880	404	38	145	1	1	4.7	1.5	30	0.01
KL36-03	97.8	99.5	0.0195		195	0.11	1.5	1210	550	77	63	3	1	3.1	2.0	40	0.01
KL36-03	99.5	101.7	0.0164		164	0.32	7.3	3600	3500	120	96	12	1	5.2	7.5	37	0.01
KL36-03	101.7	104.7	0.0143		143	0.13	1	780	520	55	60	2	1	2.1	1.4	32	0.01
KL36-03	104.7	107.7	0.0081		81	0.01	0.6	365	312	34	610	0.01	1	3.4	1.3	28	0.01
KL36-03	107.7	109.7	0.0085		85	0.02	0.8	450	410	28	650	1	1	2.3	1.8	20	0.01
KL36-03	109.7	112	0.0108		108	0.03	0.5	270	180	22	296	2	1	1.6	2.0	28	0.01
KL36-03	112	114.6	0.049		490	0.2	3.3	950	410	240	2000	18	5	10	13.3	57	0.1
KL36-03	114.6	117.2	0.0375		375	0.35	2.7	3400	850	170	370	11	8	9.1	14.0	66	0.11
KL36-03	117.2	121.3	0.075		750	0.68	9.7	11800	6400	280	920	12	7	45	16.0	43	0.34
KL36-03	121.3	123.3	0.045		450	0.26	3.2	3700	1040	130	368	13	3	10.8	9.3	54	0.13
KL36-03	123.3	125.7	0.082		820	0.33	23.8	29400	26000	140	217	23	1	35	25.5	28	0.27
KL36-03	125.7	128.7	0.0348		348	0.11	5.5	4400	4200	90	50	10	1	8.8	9.5	25	0.01
KL36-03	128.7	130.2	0.0171		171	0.09	8.8	1520	3000	52	29	19	1	5	38.5	27	0.01
KL36-03	130.2	132.7	0.015		150	0.1	3.1	1130	1200	30	26	6	1	2.2	11.8	28	0.01
KL36-03	132.7	134.2	0.0087		87	0.05	1	560	358	23	40	2	1	1.5	3.0	27	0.01
KL36-03	134.2	136.7	0.0087		87	0.08	1.5	1130	460	32	25	6	1	1.5	2.8	27	0.01
KL36-03	136.7	139.2	0.048		480	0.07	1	900	361	25	15	3	2	0.7	3.3	28	0.01
KL36-03	139.2	141.7	0.0302		302	0.1	1.3	1450	570	30	22	2	1	2.3	2.8	27	0.01
KL36-03	141.7	143.7	0.055		550	0.47	3.8	5800	1650	230	430	10	6	11.6	12.0	70	0.01
KL36-03	143.7	146.7	0.043		430	0.44	8.6	10000	4600	120	1200	22	5	14.7	14.2	25	0.01
KL36-03	146.7	149.7	0.095		950	0.76	36	49900	38100	540	58	24	8	90	35.0	25	0.28
KL36-03	149.7	152.7	0.1		1000	0.56	10.4	25000	8900	160	129	25	14	25	18.0	24	0.14
KL36-03	152.7	155	0.0076		76	0.13	3.1	2330	970	40	37	11	1	3.2	4.3	14	0.01
KL36-03	155	158	0.0301		301	0.24	5.6	8600	3500	120	48	35	1	22	6.8	17	0.01
KL36-03	158	161	0.0279		279	0.21	5.9	6900	2050	130	114	31	1	7.3	8.4	15	0.01
KL36-03	161	164.7	0.026		260	0.13	2.9	4800	1300	120	73	10	1	4.3	4.3	18	0.01
KL36-03	164.7	167.7	0.168		1680	0.52	4.5	3500	1140	78	67	10	7	2.3	9.3	18	0.01
KL36-03	167.7	170.2	0.041		410	0.12	2.4	1970	1100	74	26	8	3	2.7	7.5	15	0.01
KL36-03	170.2	171.4	0.048		480	0.12	3.8	4800	1510	98	20	11	5	3.6	6.8	13	0.01
KL36-03	171.4	173.7	0.078		780	0.18	8	9000	2400	160	45	18	8	6.1	8.6	13	0.01
KL36-03	173.7	175.3	0.0291		291	0.1	4.3	5100	1120	95	48	18	1	2.7	5.3	14	0.01
KL36-03	175.3	177.9	0.0299		299	0.11	4.2	6900	2200	140	86	15	1	3.2	6.0	16	0.01
KL36-03	177.9	179.3	0.015		150	0.05	2.4	1210	760	50	71	6	1	1.6	2.3	16	0.01
KL36-03	179.3	181.6	0.32		3200	0.27	165	112000	151000	640	153	115	7	160	27.0	25	0.16
KL36-03	181.6	183.4	0.0203		203	0.07	1.9	1700	480	94	50	12	1	2.7	4.0	16	0.01
KL36-03	183.4	185.7	0.0242		242	0.07	2.1	1710	670	77	56	19	1	2.1	4.5	16	0.01
KL36-03	185.7	188.7	0.0248		248	0.12	4.4	2600	1060	90	43	19	1	2.2	5.5	15	0.01
KL36-03	188.7	191.7	0.0187		187	0.14	4.9	2190	1220	74	50	18	1	2.1	6.5	14	0.01
KL36-03	191.7	194.7	0.082		820	0.47	2.9	4300	820	54	178	7	4	1.8	7.3	20	0.01
KL36-03	194.7	197.7	0.348		3480	1.11	5.6	5900	800	92	159	13	20	3.3	12.3	27	0.01
KL36-03	197.7	200.7	0.147		1470	0.71	14.5	20600	3200	150	66	57	15	3.2	14.5	22	0.1
KL36-03	200.7	203.7	0.118		1180	0.68	16.4	31900	2700	140	57	62	4	3.4	22.0	16	0.01
KL36-03	203.7	206.7	0.39		3900	2.55	12	25800	930	160	184	106	41	5.4	47.0	51	0.01
KL36-03	206.7	209.7	1.62		16200	1.5	21.6	1030	450	82	320	16	54	1.5	45.0	30	0.01
KL36-03	209.7	212.7	0.72		7200	1.27	20	6600	2700	120	148	13	43	4.7	22.4	25	0.01
KL36-03	212.7	215.7	1.5		15000	1.51	24.3	2800	1050	91	195	6	60	4.1	27.0	28	0.01
KL36-03	215.7	218.7	2.14		21400	2.67	34	3500	1950	72	141	7	55	3.8	22.0	30	0.01
KL36-03	218.7	221.7	2.18		21800	2.03	29.9	1770	1050	65	144	8	55	2.3	37.0	26	0.01
KL36-03	221.7	223.6	3.36		33600	3.36	32	1240	171	100	231	25	85	2.4	13.0	64	0.01
KL36-03	223.6	226.7	1.73		17300	1.45	11.1	770	257	27	56	8	42	1.9	24.0	31	0.01
KL36-03	226.7	228.7	1.06		10600	1.29	11.5	900	347	100	358	36	51	2.3	38.0	28	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL36-03	228.7	230.7	0.67	6700	0.85	3.8	3100	1580	320	1700	22	14	4.1	25.8	95	0.38
KL36-03	230.7	233.7	0.29	2900	0.62	2.5	6300	3700	950	2400	6	16	12.6	26.1	128	1.16
KL36-03	233.7	236.7	0.268	2680	0.5	2.3	4800	1600	470	1500	11	12	6	16.0	80	0.47
KL36-03	236.7	239.7	0.57	5700	0.34	4.2	550	240	23	410	3	17	1.9	17.5	30	0.01
KL36-03	239.7	242	0.91	9100	0.85	8.2	281	117	62	178	12	38	2.5	28.5	36	0.01
KL36-03	242	243.5	0.59	5900	0.64	3.1	110	57	41	32	6	19	2.1	25.6	28	0.01
KL36-03	243.5	245.7	0.985	9850	1	4.8	293	154	51	124	5	24	2.7	26.0	29	0.01
KL36-03	245.7	248.7	1.11	11100	1.08	5.8	418	203	36	180	5	25	2	19.8	26	0.01
KL36-03	248.7	251.7	0.71	7100	0.4	4.5	990	470	17	56	3	23	3	15.0	25	0.01
KL36-03	251.7	254	0.81	8100	0.51	5.3	210	116	26	500	3	21	2	8.5	24	0.01
KL36-03	254	257	1.1	11000	0.69	11.2	110	71	26	82	8	49	1.6	11.5	20	0.01
KL36-03	257	258.5	1.37	13700	0.55	17	86	61	19	172	34	24	1.6	7.0	13	0.01
KL36-03	258.5	260.7	0.92	9200	0.52	7.7	3800	440	120	260	2	20	2	9.8	43	0.01
KL36-03	260.7	263.7	1.85	18500	1.17	17.8	8200	740	310	214	5	37	2	24.5	38	0.01
KL36-03	263.7	266.7	1.11	11100	0.61	7.8	3850	570	89	3100	3	29	1.4	16.0	69	0.01
KL36-03	266.7	269.7	0.48	4800	0.32	2.3	315	140	24	252	1	23	1.5	10.8	29	0.01
KL36-03	269.7	272.7	0.147	1470	0.14	1.2	148	80	15	230	2	24	1.3	7.8	24	0.01
KL36-03	272.7	275.7	0.86	8600	0.65	9.8	270	172	34	112	18	42	2.4	14.0	29	0.01
KL36-03	275.7	278.5	1.38	13800	1.09	24.6	1500	123	16	56	25	42	2.1	19.5	38	0.01
KL36-03	278.5	281.5	1.3	13000	0.93	19.8	1740	193	41	58	20	43	2.2	19.0	44	0.01
KL36-03	281.5	284.5	1.76	17600	1.15	22.5	1150	117	43	940	21	48	4.1	24.0	33	0.01
KL36-03	284.5	287.6	2.78	27800	1.63	9.1	184	66	22	119	10	49	3	15.0	36	0.01
KL36-03	287.6	290.6	2.23	22300	1.13	6.8	98	83	21	7	4	63	2.7	16.5	30	0.01
KL36-03	290.6	293.7	2.1	21000	0.83	5.4	221	206	42	4	7	51	2.6	18.0	41	0.1
KL36-03	293.7	296.7	1.47	14700	0.71	3.6	98	76	18	11	8	42	2	22.5	62	0.01
KL36-03	296.7	299.7	1.87	18700	1.09	5.9	100	49	13	12	9	40	1.4	16.0	45	0.01
KL36-03	299.7	302.7	2.7	27000	1.25	7.5	253	62	13	9	7	59	1.7	12.0	47	0.01
KL36-03	302.7	305.7	1.93	19300	1.12	5.9	172	42	7	7	4	51	1.7	11.5	43	0.01
KL36-03	305.7	308.7	2.21	22100	1.67	6.1	83	57	7	14	3	45	1.1	6.0	33	0.01
KL36-03	308.7	311.7	3.16	31600	2.24	8.1	108	34	9	52	2	46	0.8	13.0	28	0.01
KL36-03	311.7	314.7	2	20000	2.37	5.1	76	46	15	303	3	52	2	11.5	48	0.01
KL36-03	314.7	317.7	1.74	17400	1.07	5	1220	214	1560	10	6	65	4.5	42.0	61	0.8
KL36-03	317.7	320	1.56	15600	0.55	3.1	1390	247	120	209	3	67	2	42.5	51	0.5
KL36-03	320	321.5	0.6	6000	0.27	1.1	363	108	55	382	2	45	1	16.0	41	0.15
KL36-03	321.5	323.7	0.88	8800	0.28	1.5	640	177	48	376	0.01	54	0.8	14.3	55	0.18
KL36-03	323.7	326.7	0.68	6800	0.28	1.3	550	112	40	101	3	54	0.8	43.5	108	0.14
KL36-03	326.7	329.7	1.3	13000	0.23	2.7	1140	172	31	200	1	47	0.8	23.5	101	0.25
KL36-03	329.7	332.7	1.24	12400	0.41	2.7	740	101	200	375	2	117	1.9	22.0	134	0.22
KL36-03	332.7	335.7	1.46	14600	0.75	4.7	1720	316	1420	360	4	116	60	28.0	98	0.48
KL36-03	335.7	338.7	0.0214	214	0.23	1.1	189	84	110	171	13	1	8.4	4.3	54	0.01
KL36-03	338.7	341	1.04	10400	0.48	2.6	2350	366	160	310	4	168	5.7	33.5	95	0.24
KL36-03	341	343.7	1.3	13000	0.38	3.2	3400	460	33	551	2	230	0.6	32.5	79	0.2
KL36-03	343.7	345.7	1.38	13800	0.36	2.8	800	127	31	270	1	159	0.7	23.5	76	0.11
KL36-03	345.7	347.7	1.32	13200	0.37	3.1	1360	123	22	174	0.01	145	0.6	17.5	70	0.16
KL36-03	347.7	350.7	1.38	13800	0.57	3.4	399	52	16	231	0.01	106	0.5	27.5	79	0.15
KL36-03	350.7	353.7	1.28	12800	0.16	3	297	32	12	164	0.01	120	0.4	25.0	96	0.12
KL36-03	353.7	356.3	0.87	8700	0.29	1.6	2100	560	37	243	0.01	95	0.7	32.5	93	0.18
KL36-03	356.3	358.9	0.94	9400	0.24	1.5	2350	450	40	235	0.01	90	0.6	22.2	94	0.13
KL36-03	358.9	360.9	1.41	14100	0.19	2.8	1930	460	18	224	0.01	67	0.5	24.5	94	0.17
KL36-03	360.9	362.7	1.54	15400	0.13	2.8	1090	251	51	267	0.01	106	4.3	37.5	84	0.15
KL36-03	362.7	364.5	1.87	18700	0.14	3.2	161	86	29	364	0.01	60	0.2	23.0	95	0.1
KL36-03	364.5	367.6	1.06	10600	0.13	2.1	700	206	46	167	0.01	45	0.7	19.0	93	0.11
KL36-03	367.6	370.1	1.15	11500	0.14	2.1	297	72	260	320	0.01	27	3.4	12.5	113	0.12
KL36-03	370.1	373.1	1.05	10500	0.14	2.4	233	181	59	162	0.01	56	0.4	18.0	94	0.1
KL36-03	373.1	376.2	1.02	10200	0.11	3.8	372	365	130	320	0.01	53	2.2	18.5	93	0.11
KL36-03	376.2	377.7	1.07	10700	0.1	3.8	155	440	220	330	0.01	50	1.8	14.5	99	0.1
KL36-03	377.7	380.7	1.62	16200	0.17	4.8	1220	210	1640	400	2	56	6.5	20.0	84	0.28
KL36-03	380.7	383.7	1.01	10100	0.32	4.6	4360	1230	540	361	1	54	3.5	20.0	62	0.3
KL36-03	383.7	386.3	1.3	13000	0.27	4	590	309	280	184	2	61	8.3	22.0	85	0.21
KL36-03	386.3	389.2	1.07	10700	0.19	3	610	229	98	195	1	60	3.4	22.4	85	0.15
KL36-03	389.2	391	1.02	10200	0.31	2.7	2290	400	310	512	2	43	5.1	32.0	65	0.3
KL36-03	391	392.7	0.46	4600	0.13	1.4	1940	410	37	271	0.01	47	2	13.0	67	0.2
KL36-03	392.7	395.7	0.54	5400	0.14	1.4	990	218	40	400	0.01	30	2.3	12.9	86	0.1

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL36-03	395.7	398.7	1.04	10400	0.17	2.1	740	153	30	187	0.01	23	0.6	11.5	81	0.13
KL36-03	398.7	401.7	0.89	8900	0.12	2	1220	197	11	254	0.01	25	0.2	10.0	84	0.14
KL36-03	401.7	404.7	0.74	7400	0.18	1.5	1550	264	9	101	0.01	29	0.2	11.3	74	0.13
KL36-03	404.7	407.7	0.97	9700	0.13	1.7	900	161	23	600	0.01	27	0.3	11.6	78	0.11
KL36-03	407.7	410.7	1.28	12800	0.13	2	1010	850	43	102	0.01	24	0.5	19.5	66	0.2
KL36-03	410.7	413.7	0.85	8500	0.19	1.4	1720	870	25	307	1	24	0.2	10.0	81	0.26
KL36-03	413.7	416.4	1.04	10400	0.18	1.8	660	94	61	150	2	24	0.4	15.5	88	0.25
KL36-03	416.4	419.5	0.93	9300	0.16	2	399	117	49	305	4	26	1	17.5	96	0.14
KL36-03	419.5	422.5	1.04	10400	0.17	2.7	430	107	180	117	2	28	4.5	23.5	98	0.2
KL36-03	422.5	425.5	0.88	8800	0.2	2.3	750	165	150	170	2	27	4.3	14.5	96	0.25
KL36-03	425.5	428.1	1.6	16000	0.15	3.3	105	65	30	54	2	25	0.5	26.0	136	0.16
KL36-03	428.1	429.7	0.66	6600	0.13	2.4	1530	420	180	238	0.01	15	9.9	7.0	81	0.29
KL36-03	429.7	431.7	0.9	9000	0.52	4.5	2620	510	110	180	4	28	6.1	13.0	63	0.33
KL36-03	431.7	434.7	1.1	11000	0.17	2.1	760	226	66	140	1	20	1	13.0	91	0.24
KL36-03	434.7	437.7	0.95	9500	0.1	2.3	86	80	54	154	1	20	1.4	10.5	89	0.13
KL36-03	437.7	440.7	0.95	9500	0.07	1.8	223	121	51	202	1	25	0.7	18.0	83	0.35
KL36-03	440.7	442.4	1.33	13300	0.15	3.9	301	133	40	114	1	24	0.6	22.0	94	0.4
KL36-03	442.4	444	1.41	14100	0.25	5	89	68	7	46	1	36	1	41.0	94	0.21
KL36-03	444	446.3	1.64	16400	0.32	8.4	130	74	47	66	2	53	1.1	49.0	82	0.56
KL36-03	446.3	449.4	1.99	19900	1.14	11.4	220	196	520	43	4	40	12	39.0	104	0.55
KL36-03	449.4	451.2	1.9	19000	0.79	9	56	49	7	30	3	29	0.3	42.8	88	0.01
KL36-03	451.2	452.3	2.1	21000	1.01	12.4	73	49	16	27	1	28	0.6	37.5	121	0.01
KL36-03	452.3	455.1	2.19	21900	0.5	7.3	65	39	35	107	1	44	0.4	30.5	92	0.18
KL36-03	455.1	456.5	1.51	15100	0.56	8.2	298	500	1060	193	1	52	13.5	28.5	130	0.72
KL36-03	456.5	458.7	1.55	15500	0.91	8.3	320	283	750	479	1	89	9	40.0	149	0.69
KL36-03	458.7	461.7	0.67	6700	0.66	4.3	870	1400	420	172	1	52	6.4	32.8	129	0.51
KL36-03	461.7	464.7	0.61	6100	0.27	2.5	415	194	95	188	1	47	1.2	46.0	111	0.16
KL36-03	464.7	467.7	0.99	9900	0.8	10.1	990	500	1510	152	1	19	9.6	14.5	164	0.89
KL36-03	467.7	470.7	1.75	17500	0.98	6.8	1030	880	1580	470	1	52	4.3	24.5	115	0.8
KL36-03	470.7	473.7	2.96	29600	0.97	10.6	2000	530	520	750	3	32	1.8	19.0	126	0.72
KL36-03	473.7	475.7	2.95	29500	1.75	13.5	6300	1030	530	368	3	56	7.6	24.0	167	0.93
KL36-03	475.7	477.7	1.63	16300	2.43	16.8	1030	1000	2100	7	22	93	35	13.0	76	1.61
KL36-03	477.7	479.7	0.86	8600	0.88	3.1	335	50	34	4	11	130	1.1	9.0	69	0.01
KL36-03	479.7	482.7	2.2	22000	1.5	6	850	71	16	14	6	103	0.9	12.5	56	0.01
KL36-03	482.7	485.7	1.42	14200	1.23	6	930	230	28	120	7	56	1.8	7.5	64	0.01
KL36-03	485.7	488.7	1.64	16400	1.2	6.1	1530	650	64	4	3	92	7.7	18.5	71	0.01
KL36-03	488.7	491.7	2.23	22300	1.29	16.1	1730	1140	180	5	6	75	3.8	27.5	131	0.1
KL36-03	491.7	494.7	3.33	33300	1.32	21.4	2840	2220	91	22	11	82	2.5	38.0	128	0.79
KL36-03	494.7	497.7	2.06	20600	1.17	14	2660	1810	43	213	23	65	4.1	32.5	94	0.47
KL36-03	497.7	500.7	3.4	34000	2.25	8.9	440	70	2	8	4	46	1.1	13.0	40	0.01
KL36-03	500.7	503.7	1.83	18300	1.62	6.5	190	26	12	10	12	51	2	25.5	37	0.01
KL36-03	503.7	506.7	1.22	12200	1.34	4	140	18	8	11	4	46	2.7	19.3	35	0.01
KL36-03	506.7	509.7	4.12	41200	1.81	12.6	288	43	2	7	2	36	1	8.0	29	0.01
KL36-03	509.7	512.7	1.33	13300	0.58	2.9	88	16	4	12	2	24	1.4	19.5	26	0.01
KL36-03	512.7	515.7	0.38	3800	0.42	1.7	60	7	6	46	1	25	15.9	24.2	26	0.01
KL36-03	515.7	518.7	0.68	6800	0.64	3.4	52	15	9	30	3	48	0.8	57.0	45	0.01
KL36-03	518.7	520.6	0.54	5400	0.54	2.3	51	12	9	25	3	35	1.5	21.9	49	0.01
KL36-03	520.6	522.7	1.23	12300	0.87	3.1	69	11	14	86	0.01	46	1	31.8	38	0.01
KL36-03	522.7	524.7	0.96	9600	0.71	2.5	68	14	18	42	0.01	21	1	8.5	36	0.01
KL36-03	524.7	527.7	1.56	15600	0.61	3.3	88	26	6	105	1	25	1	23.5	29	0.01
KL36-03	527.7	530.7	0.87	8700	0.46	2.7	69	11	8	13	0.01	16	1	7.4	17	0.01
KL36-03	530.7	533.7	1.06	10600	0.4	2.7	61	19	5	152	2	35	0.9	42.0	24	0.01
KL36-03	533.7	536.7	1.03	10300	0.52	2.8	65	18	6	54	1	33	1.1	20.7	41	0.01
KL36-03	536.7	539.7	1.02	10200	0.91	3	95	13	11	33	0.01	30	0.9	14.0	28	0.01
KL36-03	539.7	542.7	1.36	13600	1	4.6	146	24	2	156	0.01	41	0.01	22.0	19	0.01
KL36-03	542.7	545.7	1.8	18000	1.41	5	127	10	4	37	0.01	55	0.01	21.0	33	0.01
KL36-03	545.7	548.7	0.72	7200	0.57	2.7	91	10	2	13	1	16	0.01	6.9	32	0.01
KL36-03	548.7	551.7	1.38	13800	0.65	4.2	95	16	12	25	0.01	46	0.3	19.0	27	0.01
KL36-03	551.7	554.7	1.35	13500	0.78	4.3	91	10	4	29	0.01	32	0.01	13.5	19	0.01
KL36-03	554.7	557.7	0.76	7600	0.39	2.7	49	9	2	44	0.01	18	0.01	10.6	21	0.01
KL36-03	557.7	560.7	0.21	2100	0.23	1.5	45	11	4	50	0.01	25	0.01	36.0	21	0.01
KL36-03	560.7	562.5	0.22	2200	0.07	1.4	32	15	3	32	0.01	8	0.2	7.1	28	0.01
KL36-03	562.5	565.5	0.28	2800	0.15	1.6	64	30	18	31	2	24	0.4	13.5	28	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL36-03	565.5	567.6	0.157	1570	0.04	1.1	57	28	2	22	0.01	11	0.5	12.8	23	0.01
KL36-03	567.6	569.7	0.158	1580	0.06	1	32	11	0.01	9	0.01	7	0.2	4.8	12	0.01
KL36-03	569.7	572.7	0.21	2100	0.05	1.3	321	312	31	75	0.01	10	2.1	15.0	38	0.01
KL36-03	572.7	575.7	0.305	3050	0.05	1.3	48	16	2	143	0.01	24	0.3	14.4	76	0.01
KL36-03	575.7	578.7	0.24	2400	0.11	2	58	21	3	42	1	9	0.2	16.4	34	0.01
KL36-03	578.7	581	0.071	710	0.01	1	24	7	2	14	0.01	4	0.2	6.3	27	0.01
KL36-03	581	584	0.2	2000	0.07	1.6	73	31	4	18	0.01	9	0.4	6.5	33	0.01
KL36-03	584	587	0.27	2700	0.07	1.5	43	12	0.01	89	0.01	11	0.3	6.3	33	0.01
KL36-03	587	590	0.106	1060	0.09	0.7	40	10	0.01	14	0.01	14	0.01	7.8	35	0.01
KL36-03	590	593.2	0.58	5800	0.21	2.1	50	7	0.01	107	0.01	16	0.01	13.2	43	0.01
KL36-03	593.2	596.2	0.32	3200	0.34	1.6	68	10	0.01	50	0.01	8	0.2	9.5	35	0.01
KL36-03	596.2	599.3	0.34	3400	0.15	1.2	32	6	0.01	20	0.01	15	0.4	16.3	22	0.01
KL36-03	599.3	602.4	0.173	1730	0.11	1.2	27	5	0.01	22	0.01	7	0.01	10.8	29	0.01
KL36-03	602.4	605.6	0.68	6800	0.36	2.9	62	24	8	63	0.01	16	0.2	15.3	74	0.01
KL36-03	605.6	608.7	0.26	2600	0.16	1.6	39	11	2	9	0.01	10	0.01	5.8	32	0.01
KL36-03	608.7	611.7	0.23	2300	0.12	0.9	40	15	3	79	0.01	6	0.01	3.8	29	0.01
KL36-03	611.7	614.7	0.2	2000	0.12	1.3	36	12	2	19	0.01	6	0.01	5.8	25	0.01
KL36-03	614.7	617.7	0.23	2300	0.17	2.4	1640	165	23	23	6	8	0.6	7.3	19	0.01
KL36-03	617.7	620.7	0.21	2100	0.07	1.4	60	34	0.01	7	0.01	7	0.01	6.4	72	0.01
KL36-03	620.7	623.7	0.454	4540	0.29	1.6	51	8	1	49	0.01	10	0.01	6.0	31	0.01
KL36-03	623.7	626.5	0.57	5700	0.25	2.1	68	9	3	18	0.01	16	0.01	7.0	46	0.01
KL36-03	626.5	629.6	0.26	2600	0.15	1.4	57	10	5	63	0.01	9	0.2	4.5	46	0.01
KL36-03	629.6	631.6	0.154	1540	0.06	0.9	35	13	3	31	0.01	6	0.01	4.3	46	0.01
KL36-03	631.6	633.3	0.21	2100	0.07	1.2	45	12	1	37	0.01	8	0.01	6.5	33	0.01
KL36-03	633.3	635.7	0.136	1360	0.06	0.8	75	31	14	115	0.01	8	0.01	5.6	35	0.01
KL36-03	635.7	637.4	0.078	780	0.02	0.6	33	12	2	44	0.01	5	0.01	1.3	64	0.01
KL36-03	637.4	639.4	0.065	650	0.02	0.7	28	10	3	231	0.01	5	0.2	1.0	37	0.01
KL36-03	639.4	642.5	0.3	3000	0.14	1.5	75	27	3	253	1	12	0.2	7.3	59	0.01
KL36-03	642.5	644.7	0.466	4660	0.11	1.9	85	17	1	510	0.01	10	0.3	8.3	66	0.01
KL36-03	644.7	647.7	0.27	2700	0.12	1.6	87	30	14	367	0.01	14	0.2	11.8	106	0.01
KL36-03	647.7	650.7	0.109	1090	0.06	0.6	51	16	9	104	0.01	16	0.01	2.3	31	0.01
KL36-03	650.7	653.7	0.482	4820	0.27	1.7	151	56	34	137	2	25	0.7	12.7	81	0.01
KL36-03	653.7	655.6	0.061	610	0.03	0.6	61	17	3	38	0.01	13	0.2	1.5	20	0.01
KL36-03	655.6	658.7	0.163	1630	0.02	0.6	61	27	0.01	193	0.01	8	0.01	4.8	18	0.01
KL36-03	658.7	661.8	0.107	1070	0.02	0.7	118	39	12	54	0.01	12	0.01	4.8	13	0.01
KL36-03	661.8	664.9	0.17	1700	0.03	0.6	76	21	3	167	0.01	13	0.2	5.3	21	0.01
KL36-03	664.9	668	0.152	1520	0.03	0.7	80	22	3	94	0.01	15	0.01	9.8	28	0.01
KL36-03	668	669.8	0.156	1560	0.07	0.6	46	13	5	40	0.01	8	0.3	5.8	81	0.01
KL36-03	669.8	671.7	0.067	670	0.02	0.7	28	11	0.01	36	0.01	4	0.01	1.9	111	0.01
KL36-03	671.7	674.7	0.074	740	0.01	0.6	25	9	2	76	0.01	4	0.01	1.0	48	0.01
KL36-03	674.7	677.7	0.184	1840	0.04	1	45	11	0.01	39	0.01	5	0.01	3.0	60	0.01
KL36-03	677.7	680.7	0.189	1890	0.1	1	56	19	0.01	81	0.01	8	0.01	5.1	32	0.01
KL36-03	680.7	683.7	0.084	840	0.03	0.5	27	13	0.01	20	1	7	0.01	3.3	15	0.01
KL36-03	683.7	686.7	0.108	1080	0.03	1.1	91	189	0.01	38	0.01	8	0.2	6.8	14	0.01
KL36-03	686.7	689.7	0.132	1320	0.04	0.9	128	88	3	197	1	8	0.2	6.0	24	0.01
KL36-03	689.7	692.7	0.184	1840	0.05	1.1	53	24	0.01	54	0.01	8	0.01	4.0	37	0.01
KL36-03	692.7	695.7	0.26	2600	0.12	1.6	118	58	15	93	2	10	0.6	10.5	16	0.01
KL36-03	695.7	698.7	0.182	1820	0.12	1.1	38	14	0.01	30	0.01	4	0.01	2.3	7	0.01
KL36-03	698.7	700.8	0.3	3000	0.2	1	39	11	0.01	125	0.01	15	0.01	17.7	16	0.01
KL36-03	700.8	703.1	0.075	750	0.05	0.5	21	8	2	59	0.01	5	0.01	3.8	14	0.01
KL36-03	703.1	704.7	0.145	1450	0.04	0.9	20	7	0.01	70	0.01	3	0.01	1.0	9	0.01
KL36-03	704.7	707.7	1.04	10400	0.53	2.4	86	8	1	35	0.01	35	0.01	8.3	27	0.01
KL36-03	707.7	710.7	0.369	3690	0.19	1.3	50	17	5	45	0.01	9	0.01	7.8	30	0.01
KL36-03	710.7	712.8	0.25	2500	0.12	1.2	42	15	2	124	0.01	12	0.01	7.3	18	0.01
KL36-03	712.8	715.1	0.81	8100	0.47	2.3	102	60	3	114	1	19	1.3	9.9	39	0.01
KL36-03	715.1	716.7	1.37	13700	0.36	1.9	30	10	2	211	0.01	11	0.8	5.5	51	0.01
KL36-03	716.7	719.7	1.67	16700	0.92	5.3	133	13	2	7	1	44	0.01	15.5	24	0.01
KL36-03	719.7	722.7	2.78	27800	1.84	6.5	152	11	2	14	0.01	60	0.01	12.0	32	0.01
KL36-03	722.7	725.7	0.21	2100	0.11	0.9	54	9	3	37	0.01	19	0.01	6.3	21	0.01
KL36-03	725.7	728.7	0.419	4190	0.29	1.3	75	21	3	20	0.01	18	0.01	5.3	28	0.01
KL36-03	728.7	731.2	0.78	7800	0.69	2.7	105	9	2	13	0.01	25	0.5	10.0	44	0.01
KL36-03	731.2	732.8	0.67	6700	0.53	2.2	157	14	0.01	8	0.01	35	0.5	10.1	47	0.01
KL36-03	732.8	735.7	1.68	16800	1.63	5.4	161	9	3	20	0.01	45	0.5	15.5	33	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL36-03	735.7	737.7	0.487		4870	0.45	1.9	90	7	0.01	10	0.01	20	0.4	9.0	37	0.01
KL36-03	737.7	740.7	0.58		5800	0.41	2.1	89	21	3	57	0.01	24	0.2	11.9	47	0.01
KL36-03	740.7	743.7	0.433		4330	0.33	1.8	68	11	5	43	0.01	25	0.2	10.3	34	0.01
KL36-03	743.7	745.7	0.68		6800	0.49	2.3	129	50	4	55	1	24	0.4	10.5	48	0.01
KL36-03	745.7	748.4	0.63		6300	0.77	2.5	157	121	4	10	3	22	0.01	8.0	30	0.01
KL36-03	748.4	749.7	0.55		5500	0.57	2.4	69	15	5	24	2	16	0.01	6.0	35	0.01
KL36-03	749.7	752.7	0.53		5300	0.35	1.9	68	14	5	33	0.01	25	0.01	14.5	45	0.01
KL36-03	752.7	755.5	0.51		5100	0.38	2	62	17	4	42	1	25	0.01	12.5	26	0.01
KL36-03	755.5	758.5	0.2		2000	0.07	1	39	9	0.01	27	1	12	0.01	8.0	15	0.01
KL36-03	758.5	761.5	0.115		1150	0.03	0.8	33	7	2	71	0.01	9	0.01	3.8	31	0.01
KL36-03	761.5	762.8	0.385		3850	0.23	1.3	64	9	0.01	140	0.01	28	0.01	8.5	25	0.01
KL36-04	0	5	0.0034		34	0.02	0.1	116	51	2	1	0.01	1	0.5	0.9	10	0.01
KL36-04	5	8	0.0023		23	0.05	0.1	134	72	6	1	0.01	1	0.7	1.7	15	0.01
KL36-04	8	11	0.0022		22	0.04	0.1	215	136	5	1	0.01	1	1	1.6	13	0.01
KL36-04	11	13.5	0.0039		39	0.08	2.8	670	570	10	1	0.01	1	2.4	2.4	17	0.01
KL36-04	13.5	16.5	0.0032		32	0.05	0.5	165	47	7	2	0.01	1	0.8	1.0	16	0.01
KL36-04	16.5	18	0.0057		57	0.07	1.1	274	110	15	2	0.01	1	2.3	2.8	23	0.01
KL36-04	18	20	0.0046		46	0.05	0.1	159	35	6	3	0.01	1	1.2	0.8	19	0.01
KL36-04	20	23	0.0101		101	0.04	0.1	122	22	5	3	0.01	1	0.7	0.8	18	0.01
KL36-04	23	26	0.0038		38	0.03	0.1	170	112	8	2	0.01	2	1.4	1.2	24	0.01
KL36-04	26	29	0.0076		76	0.06	1	372	331	12	5	0.01	1	1.7	3.2	21	0.01
KL36-04	29	32	0.0031		31	0.04	0.1	114	38	7	3	0.01	1	1.4	1.3	22	0.01
KL36-04	32	35	0.03		300	0.05	0.5	212	52	15	6	0.01	1	1.2	1.6	19	0.01
KL36-04	35	38	0.0032		32	0.01	0.1	35	21	13	3	0.01	1	0.5	1.0	26	0.01
KL36-04	38	41	0.0023		23	0.04	0.1	119	25	11	3	0.01	1	1.4	1.2	24	0.01
KL36-04	41	44	0.0048		48	0.08	0.6	279	76	12	2	0.01	1	1.6	1.2	26	0.13
KL36-04	44	47	0.0076		76	0.06	0.1	231	79	7	1	0.01	1	1.5	1.8	25	0.1
KL36-04	47	50	0.0074		74	0.04	0.1	81	24	10	2	0.01	2	1.3	1.1	29	0.01
KL36-04	50	53	0.0045		45	0.14	0.5	108	23	10	2	0.01	1	1.3	1.9	38	0.1
KL36-04	53	56	0.0039		39	0.06	0.1	71	37	11	2	0.01	1	1.4	1.6	30	0.01
KL36-04	56	59	0.0093		93	0.05	1.2	460	294	28	1	0.01	1	14	10.0	27	0.01
KL36-04	59	61	0.0029		29	0.03	0.1	51	17	14	1	0.01	1	0.8	1.4	22	0.01
KL36-04	61	64	0.004		40	0.01	0.1	18	11	9	3	0.01	1	0.5	0.9	25	0.01
KL36-04	64	67.1	0.0049		49	0.02	0.1	28	16	12	2	0.01	1	0.6	0.6	26	0.01
KL36-04	67.1	70.2	0.0033		33	0.04	0.1	48	17	7	2	0.01	1	0.7	1.5	20	0.01
KL36-04	70.2	73.3	0.0011		11	0.06	0.1	84	53	12	3	0.01	1	1.5	1.2	39	0.01
KL36-04	73.3	75.4	0.0041		41	0.08	0.1	123	83	14	2	0.01	1	1	2.8	28	0.01
KL36-04	75.4	77	0.0074		74	0.04	0.1	33	18	9	2	0.01	1	4.9	1.3	36	0.01
KL36-04	77	80	0.0012		12	0.01	0.1	78	94	8	1	0.01	1	1.1	1.3	32	0.01
KL36-04	80	83	0.0038		38	0.1	0.1	34	19	13	1	0.01	1	0.9	1.5	31	0.1
KL36-04	83	86	0.0024		24	0.03	0.1	42	19	12	2	0.01	1	0.9	1.9	28	0.01
KL36-04	86	88.5	0.0052		52	0.04	0.1	145	38	16	7	0.01	1	2	3.5	25	0.01
KL36-04	88.5	91.5	0.0033		33	0.03	0.1	114	21	10	6	1	1	0.7	2.0	25	0.01
KL36-04	91.5	93.8	0.0057		57	0.1	0.1	183	107	11	4	0.01	1	1.2	2.3	26	0.1
KL36-04	93.8	97.1	0.0077		77	0.09	0.1	128	48	12	3	0.01	1	1.5	1.2	23	0.01
KL36-04	97.1	99.7	0.0095		95	0.07	0.1	80	34	11	3	0.01	1	1.5	1.6	25	0.01
KL36-04	99.7	101	0.0068		68	0.08	0.1	142	31	7	4	0.01	1	1	1.7	27	0.01
KL36-04	101	103.8	0.0073		73	0.08	0.1	116	45	12	4	0.01	1	1.4	1.6	32	0.01
KL36-04	103.8	106.6	0.0088		88	0.12	0.7	199	85	11	3	0.01	1	1.8	1.4	33	0.01
KL36-04	106.6	110	0.0021		21	0.1	0.5	149	63	11	3	0.01	1	1.9	1.4	43	0.01
KL36-04	110	113	0.0027		27	0.08	0.1	94	43	7	2	0.01	1	2.6	1.9	28	0.01
KL36-04	113	115.5	0.0037		37	0.09	0.1	82	38	8	3	0.01	1	2.2	1.9	21	0.01
KL36-04	115.5	117.5	0.0024		24	0.02	0.6	46	30	16	4	0.01	1	0.8	1.7	18	0.01
KL36-04	117.5	120.5	0.003		30	0.04	0.7	53	27	15	9	0.01	1	1.2	1.5	19	0.1
KL36-04	120.5	123.5	0.0027		27	0.01	0.1	34	25	14	3	0.01	1	0.9	1.6	22	0.01
KL36-04	123.5	126.4	0.0015		15	0.01	0.7	64	46	22	3	0.01	1	1.4	1.6	25	0.01
KL36-04	126.4	129	0.0014		14	0.02	0.1	28	22	6	2	0.01	1	0.8	0.9	19	0.01
KL36-04	129	132	0.0015		15	0.08	0.7	34	26	12	3	0.01	1	1.2	1.6	20	0.01
KL36-04	132	134	0.002		20	0.14	1	95	45	14	2	0.01	1	2.4	2.3	20	0.13
KL36-04	134	136.8	0.0022		22	0.14	0.8	70	45	18	2	0.01	1	2.6	2.3	19	0.15
KL36-04	136.8	140	0.002		20	0.16	1.8	124	127	29	3	0.01	1	3.9	3.0	19	0.2
KL36-04	140	142	0.0024		24	0.25	0.6	42	22	15	3	0.01	1	1.4	2.8	23	0.22
KL36-04	142	145.2	0.0052		52	0.18	0.1	29	24	18	4	0.01	1	1.6	3.4	24	0.27

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL36-04	145.2	148.3	0.0036		36	0.09	0.1	124	120	23	4	0.01	1	1.4	2.9	23	0.15
KL36-04	148.3	151.4	0.0025		25	0.05	0.7	368	297	20	3	0.01	1	1.5	6.0	21	0.1
KL36-04	151.4	154.4	0.0017		17	0.04	0.1	198	215	20	3	0.01	1	2.2	3.4	24	0.1
KL36-04	154.4	157.4	0.0037		37	0.03	0.1	71	54	19	4	0.01	1	1.4	2.8	26	0.1
KL36-04	157.4	160.4	0.0035		35	0.03	0.1	49	60	23	5	0.01	1	1.3	2.7	25	0.1
KL36-04	160.4	163.5	0.0043		43	0.18	0.1	68	60	36	4	1	1	4.3	2.4	28	0.1
KL36-04	163.5	166.6	0.0022		22	0.06	0.1	30	23	18	3	0.01	1	1.3	1.7	23	0.1
KL36-04	166.6	169.6	0.0118		118	0.25	2.4	339	480	47	4	6	6	16.1	18.0	40	0.1
KL36-04	169.6	172.6	0.0016		16	0.08	3.6	97	81	25	2	0.01	1	4	1.8	26	0.12
KL36-04	172.6	175.7	0.0025		25	0.38	5.1	90	54	42	4	0.01	1	4.1	8.4	33	0.17
KL36-04	175.7	179	0.0016		16	0.43	1.7	68	68	31	4	0.01	1	5.3	3.0	29	0.14
KL36-04	179	182	0.0008		8	0.25	0.1	27	32	21	2	0.01	1	2.4	3.9	26	0.11
KL36-04	182	185	0.0058		58	0.18	2.4	59	96	35	3	0.01	1	9.8	3.9	25	0.12
KL36-04	185	188	0.0026		26	0.3	0.8	55	95	40	4	0.01	1	3.2	3.7	30	0.2
KL36-04	188	191	0.0013		13	0.2	0.1	54	83	18	2	0.01	1	1.7	2.1	29	0.1
KL36-04	191	194	0.0031		31	0.11	0.8	73	112	23	3	1	3	2.2	3.1	34	0.01
KL36-04	194	197	0.0021		21	0.32	0.7	46	63	32	3	2	3	1.3	4.1	40	0.11
KL36-04	197	199	0.0016		16	0.3	0.6	42	64	70	4	1	1	2.9	2.1	39	0.11
KL36-04	199	202	0.0017		17	0.29	0.6	98	174	34	3	0.01	1	1.6	2.4	27	0.1
KL36-04	202	204.7	0.0014		14	0.61	0.6	49	62	32	2	0.01	1	1.7	2.4	26	0.15
KL36-04	204.7	207.7	0.0099		99	0.6	1.7	201	173	49	3	3	1	8.2	5.7	31	0.1
KL36-04	207.7	210.5	0.0014		14	0.54	2.1	192	750	50	3	2	1	2.5	3.1	40	0.2
KL36-04	210.5	213.6	0.0048		48	0.49	1.7	124	730	90	3	1	1	2.5	15.3	43	0.11
KL36-04	213.6	216.7	0.008		80	0.74	1.7	238	560	110	4	2	1	3.8	6.6	36	0.19
KL36-04	216.7	219.1	0.012		120	1.21	3	630	378	180	6	7	4	13.7	11.5	63	0.27
KL36-04	219.1	224	0.0319		319	1.46	23.9	8700	10900	190	60	32	4	23	64.0	49	0.21
KL36-04	224	227	0.0074		74	0.38	2.7	670	540	100	5	2	2	13.7	7.9	30	0.19
KL36-04	227	230	0.0102		102	0.29	2.3	287	319	80	7	6	6	10.1	10.5	40	0.01
KL36-04	230	233	0.0109		109	0.27	3.8	389	540	81	5	8	7	16.8	22.0	36	0.1
KL36-04	233	235.2	0.49		4900	1.6	248	165000	125000	700	26	289	26	530	2250.0	49	0.36
KL36-04	235.2	238.4	0.099		990	1.3	73	15800	14600	230	24	113	7	200	315.0	31	1.67
KL36-04	238.4	241.6	0.0202		202	0.31	5.7	870	770	91	11	9	7	17.9	22.5	30	0.11
KL36-04	241.6	244.7	0.19		1900	0.39	20.7	16000	6900	100	56	26	10	16.9	88.0	69	0.12
KL36-04	244.7	248	0.0081		81	0.28	2.7	420	570	100	19	6	6	8.3	19.5	43	0.01
KL36-04	248	251	0.144		1440	0.92	80	60700	69500	350	113	35	8	110	290.0	50	0.3
KL36-04	251	254	0.0259		259	0.57	22.8	9200	11300	240	54	28	5	27	65.0	33	0.18
KL36-04	254	257	0.206		2060	0.4	23.9	23400	9100	63	76	29	9	10.5	81.0	45	0.13
KL36-04	257	260	0.161		1610	0.92	54	12200	12700	440	92	43	8	510	140.0	64	0.8
KL36-04	260	263	0.0264		264	3.21	45	14800	14200	570	44	6	3	130	150.0	31	0.92
KL36-04	263	266	0.169		1690	4.61	120	43600	85500	560	57	16	10	340	1100.0	53	0.01
KL36-04	266	268	0.0059		59	0.22	2.1	470	366	40	3	2	3	11	11.0	26	0.1
KL36-04	268	271	0.0072		72	0.17	3.5	930	1060	51	9	3	2	15.3	24.5	21	0.1
KL36-04	271	274.2	0.0062		62	0.28	3.4	1120	800	130	4	0.01	1	6.7	12.5	18	0.22
KL36-04	274.2	277.4	0.043		430	1.24	49	20300	21400	370	26	2	3	38	340.0	32	0.65
KL36-04	277.4	280.6	0.059		590	1.13	92	23200	27200	580	73	6	3	115	200.0	62	1.82
KL36-04	280.6	283.7	0.0224		224	1.44	55	15200	13700	560	33	22	5	46	225.0	46	0.58
KL36-04	283.7	286.8	0.0154		154	0.89	24.7	10900	10100	420	28	20	5	34	173.0	33	0.23
KL36-04	286.8	289.9	0.0046		46	0.3	4.3	750	1280	290	10	0.01	4	19.4	24.1	26	0.2
KL36-04	289.9	292.9	0.0027		27	0.28	6	284	560	200	5	0.01	2	10.8	11.0	24	0.14
KL36-04	292.9	296	0.0055		55	0.49	4.5	1240	1090	310	8	0.01	2	11.2	18.8	17	0.33
KL36-04	296	299	0.0026		26	0.16	1.1	172	167	110	3	0.01	1	3.3	4.0	23	0.21
KL36-04	299	302	0.0044		44	0.35	7.4	2580	1400	180	7	0.01	1	14.4	9.5	26	1
KL36-04	302	303.4	0.006		60	0.19	9.8	4780	5000	86	4	0.01	1	18.8	4.8	17	0.78
KL36-04	303.4	306.5	0.0081		81	0.35	3	680	680	140	5	0.01	1	14.5	6.0	20	0.4
KL36-04	306.5	309.5	0.0195		195	0.52	2.3	216	180	180	5	0.01	3	7.1	6.4	23	0.3
KL36-04	309.5	312.6	0.0096		96	1.02	11.5	2600	3100	480	5	1	4	81	48.0	26	0.85
KL36-04	312.6	315.7	0.0281		281	1.47	36	11800	12000	1560	2	28	4	218	120.0	49	2.38
KL36-04	315.7	318.8	0.057		570	1.18	38	11200	6600	1350	3	5	2	169	90.0	34	1.09
KL36-04	318.8	321.9	0.0085		85	1.31	15.3	3860	2700	410	15	1	3	85	32.9	30	0.88
KL36-04	321.9	324.9	0.0034		34	0.79	4.6	780	540	130	7	0.01	1	22	13.3	24	0.27
KL36-04	324.9	328	0.0017		17	0.33	1.6	80	79	32	8	0.01	3	3.2	3.0	17	0.01
KL36-04	328	331.1	0.0064		64	1.88	11.3	1390	550	220	14	1	4	37	17.8	32	0.56
KL36-04	331.1	334.1	0.054		540	3.08	54	15600	13400	570	58	13	4	74	150.0	28	1.48

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL36-04	334.1	337.2	0.0178		178	1.75	33	8500	4700	440	22	4	3	59	61.0	37	0.81
KL36-04	337.2	340.4	0.0354		354	2.21	107	14700	13500	670	17	2	3	110	130.0	58	1.62
KL36-04	340.4	342.7	0.0053		53	0.38	3	420	331	98	5	0.01	2	96	7.5	14	0.19
KL36-04	342.7	345.9	0.0043		43	0.67	3.1	351	247	87	7	0.01	2	14.1	6.5	16	0.24
KL36-04	345.9	349	0.0045		45	0.92	4.2	341	195	170	9	0.01	3	800	10.8	18	0.51
KL36-04	349	352	0.0053		53	0.96	5.9	344	290	120	10	0.01	2	17	15.8	24	0.48
KL36-04	352	354.4	0.0032		32	0.44	3.2	178	279	50	6	0.01	1	9.5	5.8	23	0.17
KL36-04	354.4	357.5	0.0057		57	0.72	5.7	780	720	240	14	0.01	3	13.2	20.3	25	0.4
KL36-04	357.5	360.5	0.0048		48	0.43	4.8	600	620	200	10	0.01	4	13.5	15.0	25	0.38
KL36-04	360.5	363.5	0.0048		48	0.32	2.8	316	293	210	11	0.01	4	10.3	14.0	27	0.26
KL36-04	363.5	366.5	0.0073		73	0.26	8.3	1160	940	230	9	0.01	3	10.3	20.5	28	0.3
KL36-04	366.5	369.5	0.0046		46	0.21	6.1	610	880	110	10	0.01	4	7.3	18.3	24	0.2
KL36-04	369.5	372.5	0.0091		91	0.28	7.3	3510	2800	63	7	1	1	11.5	14.0	15	0.37
KL36-04	372.5	375.5	0.007		70	0.78	6.8	630	500	140	9	0.01	1	12.1	11.8	29	0.28
KL36-04	375.5	378.7	0.011		110	0.23	3.5	1480	830	84	7	0.01	2	6.3	9.3	16	0.18
KL36-04	378.7	380	0.0036		36	0.15	1.1	62	78	37	6	0.01	2	2.2	4.5	13	0.13
KL36-04	380	383	0.0361		361	0.42	5.1	1160	309	150	20	1	4	5	9.0	20	0.36
KL36-04	383	384.4	0.0087		87	0.67	2.8	375	550	120	8	1	3	8.6	9.5	20	0.37
KL36-04	384.4	387.5	0.0046		46	0.44	2.1	122	98	29	3	0.01	2	5.4	3.9	19	0.18
KL36-04	387.5	390.5	0.0053		53	0.27	4.8	278	241	36	5	1	2	4.1	7.8	14	0.17
KL36-04	390.5	393.5	0.0074		74	0.39	1.6	274	156	58	8	1	1	6.7	7.5	32	0.3
KL36-04	393.5	396.5	0.0047		47	0.26	1.3	323	250	61	7	1	1	5.7	8.3	29	0.21
KL36-04	396.5	399.5	0.0047		47	0.28	1.2	167	102	52	6	0.01	1	5.4	4.8	24	0.3
KL36-04	399.5	402.5	0.0254		254	0.26	2.9	910	259	63	14	1	1	3.5	7.5	23	0.21
KL36-04	402.5	405.5	0.0135		135	0.33	34.2	2570	2700	80	12	5	2	11.5	43.0	23	0.56
KL36-04	405.5	408.6	0.013		130	0.34	37	2430	2300	110	6	7	2	12.3	53.0	20	0.46
KL36-04	408.6	411.6	0.0076		76	0.06	1.1	379	160	24	9	1	1	2	5.0	16	0.01
KL36-04	411.6	413.1	0.0029		29	0.32	1.2	94	88	28	2	0.01	1	5.5	3.5	18	0.12
KL36-04	413.1	416	0.0226		226	0.1	3	1720	840	60	30	4	2	4	23.5	18	0.15
KL36-04	416	419	0.041		410	0.08	3.2	5380	760	68	48	4	2	3.7	13.5	18	0.24
KL36-04	419	422	0.0327		327	0.07	10.1	4060	2600	73	76	5	2	10.6	18.8	29	0.16
KL36-04	422	425	0.0231		231	0.08	2.7	1790	690	73	30	4	1	3.9	18.3	20	0.13
KL36-04	425	428	0.0315		315	0.07	7.2	4490	1100	54	40	3	3	3.1	13.5	21	0.15
KL36-04	428	431	0.046		460	0.17	3.6	3720	1200	68	87	5	4	5	18.3	20	0.11
KL36-04	431	434	0.055		550	0.07	2.2	1190	303	67	89	5	2	3	13.3	21	0.11
KL36-04	434	437	0.0147		147	0.13	57	22000	15600	120	44	2	1	42	34.5	27	0.13
KL36-04	437	439.3	0.0048		48	0.08	7.5	1370	680	52	14	0.01	1	4.8	10.5	35	0.01
KL36-04	439.3	442.4	0.0066		66	0.01	7.9	580	460	37	10	1	1	1.7	6.5	17	0.01
KL36-04	442.4	445.4	0.0128		128	0.35	6.5	3200	1480	85	39	1	1	5.6	20.7	21	0.31
KL36-04	445.4	447.7	0.0171		171	0.04	4.2	520	264	50	35	1	1	1.9	6.8	18	0.01
KL36-04	447.7	450	0.0043		43	0.08	4.5	940	440	35	8	1	1	2.7	7.8	16	0.1
KL36-04	450	452	0.0314		314	0.34	4.9	2890	1200	76	63	3	1	6.6	17.9	22	0.3
KL36-04	452	455	0.0167		167	0.13	4.7	4060	1530	63	57	6	1	4.1	24.8	17	0.11
KL36-04	455	457.3	0.0201		201	0.61	69	29200	21800	210	36	3	3	72	39.0	33	0.43
KL36-04	457.3	460.4	0.064		640	0.16	17	12800	6000	95	154	20	4	16	71.0	28	0.42
KL36-04	460.4	463	0.053		530	0.14	8.5	9300	4100	45	111	16	3	11	40.0	23	0.18
KL36-04	463	465.7	0.0085		85	0.08	3.4	1540	840	30	26	3	1	4.7	17.0	24	0.01
KL36-04	465.7	468.7	0.0191		191	0.06	2.2	1640	940	78	37	1	1	5.8	19.0	23	0.01
KL36-04	468.7	471.7	0.045		450	0.05	1.1	331	192	34	94	1	1	2.4	4.8	26	0.01
KL36-04	471.7	474.4	0.0293		293	0.05	1.2	355	344	54	40	1	1	4.1	6.5	21	0.01
KL36-04	474.4	477	0.0083		83	0.11	1	350	210	32	26	1	1	2.6	0.0	24	0.01
KL36-04	477	479	0.0084		84	0.08	0.9	415	169	24	43	1	1	2.2	9.0	27	0.01
KL36-04	479	482	0.0076		76	0.05	1	710	165	27	64	1	1	2.3	10.3	26	0.01
KL36-04	482	485	0.0187		187	0.06	0.9	520	123	30	82	1	1	1.8	7.5	26	0.01
KL36-04	485	488	0.012		120	0.13	1	970	150	41	149	5	1	2.3	8.8	25	0.01
KL36-04	488	491	0.0141		141	0.05	0.9	590	354	36	118	2	1	2.3	6.5	22	0.01
KL36-04	491	494	0.01		100	0.12	0.8	1020	237	29	43	4	1	3.2	6.8	22	0.01
KL36-04	494	496.3	0.0213		213	0.14	7.6	3060	1830	110	68	2	1	10.8	14.0	24	0.1
KL36-04	496.3	498.5	0.0031		31	0.12	1	600	690	14	10	0.01	1	1.3	2.5	28	0.01
KL36-04	498.5	501.5	0.019		190	0.21	5.4	3760	1700	110	54	3	1	8.1	12.5	22	0.1
KL36-04	501.5	504.5	0.0223		223	0.14	2.1	4910	620	77	187	16	1	3.5	21.8	30	0.1
KL36-04	504.5	507.5	0.0337		337	0.25	2.2	6200	610	120	368	20	2	4.9	26.9	34	0.13
KL36-04	507.5	510.3	0.0223		223	0.18	1.5	2650	263	80	283	11	1	1.4	18.0	30	0.1

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL36-04	510.3	512	0.0076		76	0.09	0.7	750	398	23	87	6	1	1.8	6.0	23	0.01
KL36-04	512	515	0.0097		97	0.07	1.6	2380	1600	38	159	9	1	2.8	10.0	24	0.1
KL36-04	515	517.4	0.009		90	0.08	2	2040	1230	38	131	8	1	1.8	17.5	23	0.1
KL36-04	517.4	520.4	0.0045		45	0.07	1.1	370	345	24	32	2	1	1.3	7.0	21	0.1
KL36-04	520.4	523.6	0.0034		34	0.12	1.5	580	850	43	20	3	1	1.4	9.5	23	0.1
KL36-04	523.6	525.8	0.0059		59	0.11	5.4	3170	2000	38	14	0.01	1	8.6	11.0	28	0.12
KL36-04	525.8	528.2	0.0059		59	0.04	1.5	1040	1020	25	12	0.01	1	2	7.0	22	0.1
KL36-04	528.2	530	0.0027		27	0.11	2.8	1070	850	32	6	0.01	1	3.8	11.0	18	0.2
KL36-04	530	532.7	0.0031		31	0.11	3.7	3480	2890	32	13	0.01	1	3.2	12.3	20	0.33
KL36-04	532.7	535.8	0.0019		19	0.1	3.3	930	1380	34	7	0.01	1	2	9.7	22	0.15
KL36-04	535.8	539.2	0.0036		36	0.11	5.7	3570	3300	38	2	0.01	1	7.4	10.5	22	0.15
KL36-04	539.2	542	0.004		40	0.04	1.3	1270	690	23	20	2	1	1.2	7.0	22	0.01
KL36-04	542	545	0.0047		47	0.51	2.6	364	369	63	5	0.01	1	7	8.0	31	0.18
KL36-04	545	548	0.0083		83	0.29	6.6	2210	2000	35	2	0.01	1	10.2	16.0	22	0.34
KL36-04	548	551	0.0049		49	0.08	4.5	3750	3000	33	3	0.01	1	6.4	6.3	22	0.01
KL36-04	551	554.2	0.0052		52	0.22	2.3	890	490	36	3	0.01	1	3.9	10.5	21	0.15
KL36-04	554.2	556.3	0.0021		21	0.08	1.8	273	500	43	2	1	1	2.6	11.5	18	0.01
KL36-04	556.3	559.3	0.0054		54	0.58	3.6	384	870	160	9	1	3	9.3	15.3	28	0.2
KL36-04	559.3	560.5	0.0078		78	0.05	1.1	269	311	22	1	0.01	1	1.4	7.0	17	0.01
KL36-04	560.5	562.5	0.0059		59	0.07	1	202	237	170	3	3	11	3.3	9.0	22	0.01
KL36-04	562.5	563	0.0142		142	0.26	7.7	7700	1320	240	3	4	1	40	15.8	23	0.65
KL36-05	0	2.5	0.0047		47	0.02	0.1	185	82	10	2	0.01	1	0.6	1.2	15	0.01
KL36-05	2.5	5.5	0.0051		51	0.03	0.1	177	51	9	1	0.01	1	0.6	0.6	16	0.01
KL36-05	5.5	8.5	0.0043		43	0.02	0.1	190	70	11	3	0.01	2	0.7	1.8	16	0.01
KL36-05	8.5	11.5	0.0106		106	0.02	0.1	337	115	10	5	0.01	1	0.7	1.1	36	0.01
KL36-05	11.5	14.5	0.0024		24	0.04	0.5	490	182	11	2	0.01	1	1	1.6	20	0.01
KL36-05	14.5	17.5	0.0027		27	0.02	0.1	400	143	6	5	0.01	1	1	1.4	18	0.01
KL36-05	17.5	20	0.0173		173	0.05	0.1	386	188	14	3	0.01	1	0.8	0.7	26	0.01
KL36-05	20	23	0.0076		76	0.03	0.7	361	129	11	2	0.01	2	0.9	1.3	23	0.01
KL36-05	23	26.5	0.0089		89	0.1	0.9	830	319	20	3	0.01	1	2	1.5	63	0.01
KL36-05	26.5	29.5	0.0119		119	0.07	0.6	580	332	9	6	0.01	1	1.6	1.3	34	0.01
KL36-05	29.5	32.5	0.0057		57	0.03	0.1	368	254	12	2	0.01	1	1.7	1.3	22	0.01
KL36-05	32.5	35	0.0034		34	0.02	0.1	920	316	11	1	0.01	1	3.6	1.9	22	0.01
KL36-05	35	38.1	0.0092		92	0.02	0.5	1740	520	19	5	0.01	1	5.5	1.4	20	0.01
KL36-05	38.1	41.2	0.0203		203	0.02	0.5	510	135	18	5	0.01	1	2.1	1.0	20	0.01
KL36-05	41.2	44.5	0.0057		57	0.04	0.5	1040	363	14	3	0.01	1	2.8	1.6	12	0.01
KL36-05	44.5	47.5	0.0128		128	0.01	0.1	284	121	8	4	0.01	1	0.7	1.3	17	0.01
KL36-05	47.5	50.5	0.0132		132	0.01	0.1	137	86	27	5	0.01	1	1.6	0.9	24	0.01
KL36-05	50.5	53.5	0.0103		103	0.04	1.4	1680	710	33	5	0.01	6	5	2.7	25	0.13
KL36-05	53.5	56.5	0.0051		51	0.01	0.7	510	240	18	5	0.01	2	1.5	1.5	23	0.01
KL36-05	56.5	59.5	0.0051		51	0.01	0.1	137	86	15	2	0.01	1	1.3	0.7	21	0.01
KL36-05	59.5	62.5	0.0045		45	0.01	0.7	490	410	13	2	0.01	1	0.7	1.3	18	0.01
KL36-05	62.5	65.5	0.014		140	0.12	6.6	5080	3670	35	3	6	1	16	8.5	16	0.33
KL36-05	65.5	68.5	0.0062		62	0.05	0.1	351	312	16	3	0.01	1	1.8	1.0	20	0.01
KL36-05	68.5	71.5	0.0033		33	0.01	0.1	86	96	11	1	0.01	1	0.7	0.5	18	0.01
KL36-05	71.5	74.3	0.0028		28	0.15	0.1	175	138	20	1	0.01	1	0.9	2.2	17	0.01
KL36-05	74.3	77	0.0029		29	0.14	0.1	650	229	19	3	0.01	1	2	3.0	16	0.01
KL36-05	77	79.2	0.005		50	0.05	1.1	730	348	28	3	2	1	1.9	4.1	29	0.01
KL36-05	79.2	80.5	0.0042		42	0.07	1.3	850	460	26	1	2	1	1.9	3.8	26	0.1
KL36-05	80.5	83	0.0067		67	0.08	3.3	590	740	67	5	6	1	3.4	5.7	28	0.01
KL36-05	83	85.3	0.0146		146	0.71	7.2	2190	980	19	22	25	1	4.1	5.0	22	0.24
KL36-05	85.3	86.5	0.0078		78	0.08	1.7	1180	950	49	4	5	1	5.7	4.7	26	0.01
KL36-05	86.5	89.5	0.0054		54	0.02	0.7	184	132	38	3	2	1	1.8	2.6	29	0.01
KL36-05	89.5	92.5	0.0104		104	0.02	1.5	330	221	52	9	5	1	1.5	5.1	25	0.01
KL36-05	92.5	95.5	0.0156		156	0.08	0.6	206	95	40	38	9	1	3.2	2.9	57	0.01
KL36-05	95.5	98.5	0.118		1180	0.1	0.8	153	60	55	45	1	8	3.8	1.6	97	0.01
KL36-05	98.5	101.5	0.053		530	0.02	0.1	450	121	60	10	1	3	4.2	1.2	76	0.01
KL36-05	101.5	102.6	0.0162		162	0.1	1.2	1510	1310	48	14	2	1	4.8	3.6	84	0.1
KL36-05	102.6	104.5	0.667		6670	0.59	36.4	21900	43700	1380	72	17	10	140	20.9	78	0.71
KL36-05	104.5	107.5	1.09		10900	1.32	43.6	26200	22700	2075	138	75	12	260	17.3	80	1.64
KL36-05	107.5	110.5	0.0197		197	0.4	9.3	4510	3890	110	102	17	14	19.1	14.7	118	0.26
KL36-05	110.5	113.5	0.044		440	0.12	1.2	2310	1020	52	43	1	1	5.4	2.5	136	0.11
KL36-05	113.5	118.2	0.0081		81	0.09	1.1	2400	820	32	29	1	1	2.3	1.7	133	0.11

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL36-05	118.2	120.7	0.0299		299	0.05	0.1	500	135	49	113	0.01	1	2.3	1.4	50	0.01
KL36-05	120.7	122.5	0.0118		118	0.05	0.1	580	162	32	71	0.01	1	1.7	1.2	91	0.01
KL36-05	122.5	125.5	0.046		460	0.09	0.1	1190	470	32	170	1	1	2.3	2.0	57	0.01
KL36-05	125.5	128.5	0.0137		137	0.04	0.1	319	170	34	480	0.01	1	2.1	2.2	33	0.01
KL36-05	128.5	131.5	0.056		560	0.12	14.3	8500	1330	73	55	66	6	30	24.0	25	0.12
KL36-05	131.5	134.5	0.141		1410	0.13	1.9	1470	450	250	1190	7	5	5	5.0	27	0.01
KL36-05	134.5	137.5	0.0068		68	0.06	0.1	347	126	24	385	0.01	1	2	1.8	34	0.01
KL36-05	137.5	140.5	0.442		4420	0.53	10.7	6300	980	140	392	36	24	7.1	7.6	87	0.01
KL36-05	140.5	143.5	0.253		2530	0.36	19	44000	2800	150	80	82	98	22	30.8	22	0.27
KL36-05	143.5	146.5	0.0281		281	0.61	6.1	1260	580	98	1430	12	3	6.3	7.4	13	0.11
KL36-05	146.5	149.5	0.0143		143	0.23	5.2	1820	1820	18	77	10	1	2.8	5.3	21	0.14
KL36-05	149.5	152.5	0.043		430	0.16	7.4	11800	2900	140	16	14	1	14.3	4.1	24	0.38
KL36-05	152.5	154.5	0.0159		159	3.93	14.6	26400	5300	100	31	8	1	17.5	7.5	26	0.78
KL36-05	154.5	157.5	0.044		440	0.43	17.6	11700	3600	130	36	12	1	28	29.6	24	0.2
KL36-05	157.5	158.9	0.014		140	0.16	3.7	2640	1030	150	32	14	1	1.9	11.6	23	0.01
KL36-05	158.9	161.5	0.0296		296	0.3	13.6	10700	25400	170	27	38	12	7.6	44.0	24	0.01
KL36-05	161.5	164.5	0.0108		108	0.04	1.3	890	430	9	39	6	1	1.6	1.6	21	0.01
KL36-05	164.5	167	0.0055		55	0.04	1.7	470	600	5	42	16	1	0.7	2.1	23	0.01
KL36-05	167	170.5	0.0227		227	0.1	9.7	31800	16000	110	92	42	1	11	8.9	22	0.1
KL36-05	170.5	173	0.0112		112	0.07	3.9	2010	1200	19	95	14	1	2.9	4.6	22	0.01
KL36-05	173	175.8	0.0089		89	0.06	3.7	2100	2610	14	44	9	1	7.5	4.2	21	0.01
KL36-05	175.8	178.3	0.0081		81	0.05	2.8	1240	1940	12	55	8	1	1.7	6.0	22	0.01
KL36-05	178.3	181.6	0.0126		126	0.03	1.4	1440	254	14	20	6	1	0.9	3.9	15	0.01
KL36-05	181.6	185.1	0.0054		54	0.02	1.2	560	540	7	9	3	1	0.8	2.0	8	0.01
KL36-05	185.1	187	0.008		80	0.03	2.3	1200	1170	9	7	3	1	1.5	2.6	11	0.01
KL36-05	187	188.5	0.0204		204	0.08	11.1	4600	1540	26	17	30	1	3.5	6.6	9	0.01
KL36-05	188.5	191.2	0.045		450	0.09	21.4	13300	11000	64	35	6	2	22	4.6	11	0.01
KL36-05	191.2	194.3	0.0078		78	0.02	3.6	490	1520	11	23	4	1	6.8	1.8	8	0.01
KL36-05	194.3	197.5	0.0088		88	0.06	1.7	420	278	18	35	4	1	3.4	2.5	12	0.01
KL36-05	197.5	200.5	0.0133		133	0.14	3	650	820	47	32	6	1	4.7	3.8	12	0.01
KL36-05	200.5	202.7	0.0112		112	0.14	1.7	480	228	40	18	6	1	3.3	2.6	9	0.01
KL36-05	202.7	205.1	0.008		80	0.05	2.2	212	146	14	23	2	1	1.9	1.3	8	0.01
KL36-05	205.1	208.5	0.075		750	0.1	1.7	480	242	110	22	2	6	5.3	2.1	15	0.01
KL36-05	208.5	209.5	0.0226		226	0.15	1.1	402	180	58	15	2	3	4.5	3.1	12	0.01
KL36-05	209.5	212.5	0.0182		182	0.04	2.4	680	570	18	20	4	1	3	1.7	9	0.01
KL36-05	212.5	215.6	0.0146		146	0.05	8.7	2220	3260	11	8	16	1	4.1	4.7	13	0.01
KL36-05	215.6	218.8	0.0119		119	0.03	5.7	3610	1170	12	7	12	1	1.5	4.7	12	0.01
KL36-05	218.8	221.6	0.0075		75	0.06	2.4	1010	500	27	15	4	1	1.6	2.7	13	0.01
KL36-05	221.6	224.5	0.0059		59	0.02	1.3	382	186	9	4	2	1	0.7	1.4	11	0.01
KL36-05	224.5	227.5	0.0085		85	0.04	2.8	840	580	21	6	6	1	1.4	3.4	12	0.01
KL36-05	227.5	230.5	0.056		560	0.08	23.2	6400	3700	110	37	39	5	14.2	8.3	21	0.01
KL36-05	230.5	233.5	0.057		570	0.09	28.9	5100	6200	84	98	64	4	12	8.6	20	0.01
KL36-05	233.5	236.5	0.051		510	0.1	24.1	4300	5700	120	48	53	7	15.6	6.3	33	0.01
KL36-05	236.5	239.5	0.0237		237	0.05	5.3	3740	2900	35	51	14	2	7.1	3.8	25	0.01
KL36-05	239.5	242.5	0.0244		244	0.16	3.2	2340	1060	170	88	11	2	9.5	6.6	54	0.01
KL36-05	242.5	245.5	0.0232		232	0.07	2.5	1440	700	28	45	6	1	3.6	7.2	31	0.01
KL36-05	245.5	248.5	0.0093		93	0.05	3	1340	1330	19	33	6	1	4.3	7.6	21	0.01
KL36-05	248.5	251.5	0.0112		112	0.03	4.1	1260	1220	18	21	9	1	4	3.7	17	0.01
KL36-05	251.5	254	0.0087		87	0.03	2.2	1220	490	11	17	12	1	1.5	3.0	12	0.01
KL36-05	254	257	0.0126		126	0.03	1.8	630	399	9	28	6	1	1.4	2.4	14	0.01
KL36-05	257	260.2	0.0211		211	0.08	3	1340	660	41	217	17	1	3.8	4.7	12	0.01
KL36-05	260.2	263.3	0.0106		106	0.05	0.6	1320	460	40	26	2	1	3.1	3.0	12	0.01
KL36-05	263.3	266.5	0.054		540	0.12	0.6	580	183	150	28	7	1	1.9	2.5	19	0.01
KL36-05	266.5	269.5	0.63		6300	0.54	6.2	890	210	140	110	15	22	5.5	9.5	30	0.01
KL36-05	269.5	272.5	0.491		4910	0.64	7.6	385	460	55	60	15	45	3.7	15.4	36	0.01
KL36-05	272.5	275.5	0.141		1410	0.59	5.5	930	1320	90	690	20	14	3.2	7.0	87	0.01
KL36-05	275.5	277.5	0.125		1250	0.26	2.4	387	180	120	890	4	13	3.8	6.0	151	0.01
KL36-05	277.5	280.3	0.141		1410	0.36	4	1750	332	210	760	5	4	10.1	7.0	70	0.01
KL36-05	280.3	282.3	0.408		4080	0.1	2.6	192	137	31	146	4	11	1.4	5.8	32	0.01
KL36-05	282.3	284.5	1.15		11500	0.52	9.1	620	140	73	91	34	30	4.4	7.0	37	0.01
KL36-05	284.5	287.5	1.16		11600	0.45	8.2	530	114	71	85	28	31	2.8	5.8	35	0.01
KL36-05	287.5	289.5	0.68		6800	0.53	9.5	620	100	60	18	7	30	1.2	10.3	30	0.01
KL36-05	289.5	293.5	0.44		4400	0.36	5.5	430	70	100	37	5	18	3.2	6.1	25	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL36-05	293.5	296.5	0.311	3110	0.33	6.3	480	163	39	15	2	9	2.1	4.5	25	0.01
KL36-05	296.5	298.5	0.42	4200	0.31	8.8	730	289	58	36	14	17	1.2	5.8	34	0.01
KL36-05	298.5	300.5	0.495	4950	0.53	8.5	640	210	61	15	5	15	2	6.5	35	0.01
KL36-05	300.5	302.2	0.73	7300	0.21	13.6	750	520	62	170	44	48	2.1	9.3	35	0.01
KL36-05	302.2	305.4	0.122	1220	0.2	2	1250	70	74	16	2	9	4.9	3.8	28	0.01
KL36-05	305.4	307.5	0.053	530	0.15	1	267	323	61	27	1	2	2.9	1.8	19	0.01
KL36-05	307.5	310.7	0.75	7500	1.12	6.9	880	376	420	9	2	49	14	8.3	27	0.01
KL36-05	310.7	313.8	0.38	3800	0.94	3.9	18600	81	440	9	1	50	11.1	12.0	21	0.01
KL36-05	313.8	317	0.645	6450	0.64	5.9	8540	362	210	69	4	53	4.2	8.8	31	0.01
KL36-05	317	320.1	1	10000	0.16	8.9	1430	630	57	80	6	42	1.4	6.5	48	0.01
KL36-05	320.1	323	1.57	15700	0.12	9.1	2000	510	95	92	7	3	2	2.0	32	0.01
KL36-05	323	326	0.056	560	0.07	2.9	780	200	62	45	8	7	0.8	3.0	40	0.01
KL36-05	326	328	0.78	7800	1.28	16.6	17700	1450	91	185	25	50	5	9.2	68	0.01
KL36-05	328	331.1	0.9	9000	1.26	17.1	14300	4800	400	55	16	80	14.9	12.3	70	0.01
KL36-05	331.1	334.2	0.23	2300	0.35	2.9	1450	700	130	19	3	10	4.5	3.0	24	0.01
KL36-05	334.2	337.3	0.126	1260	0.16	1.3	1470	900	110	7	0.01	2	2.2	3.0	15	0.01
KL36-05	337.3	338.5	1.14	11400	1.07	12.3	15700	9200	260	10	20	37	28	12.5	84	0.01
KL36-05	338.5	341.5	2.06	20600	1.78	9.9	2800	2300	160	11	4	37	28.5	15.3	46	0.01
KL36-05	341.5	344.5	2.87	28700	3	6.5	850	720	48	2	4	40	21	13.0	32	0.01
KL36-05	344.5	346.7	2.01	20100	1.7	7.4	3800	2700	380	3	5	78	30	12.5	72	0.22
KL36-05	346.7	349.7	2.33	23300	2.38	9.5	5900	4300	800	5	5	85	32	14.0	51	0.58
KL36-05	349.7	352.8	4.16	41600	2.4	21.4	14100	8500	680	13	4	77	24	16.0	90	0.76
KL36-05	352.8	353.9	2.58	25800	1.06	15.5	2720	1570	54	6	2	35	8.8	16.0	73	0.01
KL36-05	353.9	355.7	2.37	23700	0.46	16.9	10500	4400	54	227	2	35	3.7	30.0	88	0.4
KL36-05	355.7	357.5	1.73	17300	0.43	10.7	1550	140	15	57	2	16	0.5	22.3	80	0.01
KL36-05	357.5	359.5	1	10000	0.24	7.6	365	186	200	20	4	12	57	12.5	108	1.06
KL36-05	359.5	362.2	0.86	8600	0.19	4.9	256	107	120	58	4	9	11	17.3	60	0.44
KL36-05	362.2	365.3	0.74	7400	0.22	3.8	630	173	25	120	5	9	1.8	14.0	61	0.01
KL36-05	365.3	368.4	0.9	9000	0.16	2	540	129	7	26	2	10	0.9	17.0	73	0.01
KL36-05	368.4	371.5	1.11	11100	0.34	3.5	322	130	13	15	3	10	0.8	14.5	70	0.01
KL36-05	371.5	373.8	0.93	9300	0.51	77	2900	18600	170	11	5	12	319	16.8	84	0.29
KL36-05	373.8	376.1	0.21	2100	0.21	1.9	170	97	5	6	2	10	1.8	6.8	62	0.01
KL36-05	376.1	378	0.512	5120	0.26	2.3	190	67	4	12	1	6	0.6	3.5	79	0.01
KL36-05	378	381	0.503	5030	0.45	2.2	130	33	1	8	3	7	0.5	5.3	77	0.01
KL36-05	381	383.5	0.29	2900	0.15	1.9	48	34	9	6	5	6	0.6	5.5	68	0.01
KL36-05	383.5	386.5	0.26	2600	0.26	3.5	117	123	8	6	4	6	2.1	3.3	75	0.01
KL36-05	386.5	389.5	0.458	4580	0.2	2.5	80	55	41	12	3	12	4	12.0	58	0.01
KL36-05	389.5	392.5	0.378	3780	0.13	4.8	142	214	10	12	5	9	2.7	5.3	71	0.01
KL36-05	392.5	395.5	0.28	2800	0.11	2	271	36	2	8	1	5	0.3	4.3	64	0.01
KL36-05	395.5	398.2	0.21	2100	0.11	2.6	530	138	31	10	16	9	12.8	8.5	97	0.01
KL36-05	398.2	400.5	0.51	5100	0.14	3.9	400	45	10	100	4	11	0.8	11.0	73	0.01
KL36-05	400.5	402	0.376	3760	0.09	3	450	25	6	60	2	8	0.3	5.8	84	0.01
KL36-05	402	404.3	0.95	9500	0.14	5.5	189	88	16	28	8	15	0.8	29.1	75	0.01
KL36-05	404.3	407.5	0.28	2800	0.16	1.6	370	104	9	37	2	9	0.3	6.0	75	0.01
KL36-05	407.5	410.5	0.16	1600	0.13	1.7	171	85	6	15	2	5	1	3.3	79	0.01
KL36-05	410.5	412	0.382	3820	0.36	1.8	300	68	6	10	1	8	1.6	4.8	83	0.01
KL36-05	412	415	0.92	9200	3.76	15.3	36600	7500	470	12	12	14	195	31.6	71	3.4
KL36-05	415	416.9	0.86	8600	0.42	1.6	251	68	5	8	0.01	13	1	7.0	68	0.14
KL36-05	416.9	418.3	0.22	2200	0.17	1.7	213	47	5	9	1	5	0.3	3.3	91	0.01
KL36-05	418.3	420.9	0.411	4110	0.04	1.2	390	67	16	20	1	3	0.6	5.5	90	0.01
KL36-05	420.9	424	0.26	2600	0.05	1	148	90	20	24	1	3	0.4	4.5	98	0.01
KL36-05	424	425.5	0.2	2000	0.05	0.9	141	82	34	35	0.01	2	0.3	3.0	176	0.01
KL36-05	425.5	427.5	0.495	4950	0.06	1.2	106	48	6	145	0.01	3	0.4	3.9	195	0.01
KL36-05	427.5	430.5	0.25	2500	0.05	1.4	92	112	500	55	0.01	3	2.9	4.5	126	0.01
KL36-05	430.5	432	0.9	9000	0.32	2.5	1740	86	790	58	1	12	1.4	6.0	126	0.14
KL36-05	432	434.5	0.58	5800	0.13	1.7	130	26	130	61	1	8	0.3	5.8	171	0.01
KL36-05	434.5	437.5	0.34	3400	0.06	1.3	73	32	8	27	1	5	0.2	2.5	140	0.01
KL36-05	437.5	440.5	0.59	5900	0.19	4.6	90	87	95	201	0.01	4	7.7	5.3	127	0.01
KL36-05	440.5	442	0.28	2800	0.05	1.2	66	167	6	27	1	3	0.3	4.0	167	0.01
KL36-05	442	444.5	0.388	3880	0.1	1.7	167	87	54	62	0.01	2	4.8	3.5	227	0.01
KL36-05	444.5	446.5	0.488	4880	0.27	2	301	168	5	24	1	1	0.3	4.1	107	0.01
KL36-05	446.5	449.5	0.24	2400	0.05	1.1	35	26	2	25	0.01	2	0.3	2.5	127	0.01
KL36-05	449.5	452.5	0.23	2300	0.07	0.8	81	34	3	46	1	4	0.2	3.0	161	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL36-05	452.5	455.5	0.57	5700	0.05	1.4	50	12	90	38	1	2	2.9	6.0	179	0.01
KL36-05	455.5	458.5	0.86	8600	0.11	8.9	330	409	740	223	2	3	32	7.0	150	0.21
KL36-05	458.5	461.5	0.83	8300	0.06	2.8	167	60	130	85	1	9	2.9	5.5	110	0.01
KL36-05	461.5	464.5	0.66	6600	0.11	2	114	103	51	75	1	3	2.4	5.5	195	0.01
KL36-05	464.5	467.5	0.32	3200	0.06	1.2	100	110	420	95	1	1	1	3.8	125	0.01
KL36-05	467.5	470.5	0.29	2900	0.05	0.9	77	47	610	50	0.01	2	2.7	4.0	147	0.01
KL36-05	470.5	473.5	0.68	6800	0.29	2.6	70	102	1720	262	2	1	14.6	5.5	224	0.32
KL36-05	473.5	476.5	0.436	4360	0.37	2.7	56	115	1350	75	1	1	8.5	4.3	160	0.2
KL36-05	476.5	478	0.422	4220	0.19	1.1	27	78	1420	90	0.01	4	4.9	4.4	180	0.01
KL36-05	478	480.5	0.35	3500	0.07	0.1	35	61	970	40	0.01	1	2.5	3.3	137	0.01
KL36-05	480.5	482.4	0.78	7800	0.15	1.1	40	60	2120	39	0.01	4	5.7	6.4	192	0.1
KL36-05	482.4	485.5	1.14	11400	0.17	1.9	50	24	1080	221	0.01	3	2.7	5.2	168	0.01
KL36-05	485.5	488.5	0.66	6600	0.12	1.3	40	20	420	67	0.01	2	0.5	5.0	245	0.01
KL36-05	488.5	491.4	0.497	4970	0.1	0.8	26	15	52	52	0.01	2	0.3	4.3	212	0.01
KL36-05	491.4	494.5	0.68	6800	0.15	4.2	241	173	65	71	1	7	40	5.5	250	0.18
KL36-05	494.5	497.5	0.74	7400	0.24	1	30	16	2	70	0.01	5	0.4	5.8	220	0.01
KL36-05	497.5	500.5	0.61	6100	0.2	1.1	35	20	6	55	0.01	3	0.3	4.1	280	0.01
KL36-05	500.5	503.5	0.65	6500	0.24	1.7	31	39	32	51	0.01	8	0.3	5.0	221	0.01
KL36-05	503.5	506.5	0.79	7900	0.16	2	34	26	320	61	0.01	4	0.3	3.3	230	0.01
KL36-05	506.5	509.5	0.424	4240	0.12	0.9	17	10	12	68	0.01	10	0.4	2.8	250	0.01
KL36-05	509.5	512.5	0.476	4760	0.19	1.2	29	8	110	245	0.01	4	0.6	4.3	227	0.01
KL36-05	512.5	515.5	0.431	4310	0.15	1	21	15	17	59	0.01	4	0.01	3.9	187	0.01
KL36-05	515.5	518.5	0.358	3580	0.04	1	12	14	58	64	0.01	4	0.5	3.5	155	0.01
KL36-05	518.5	521.5	0.457	4570	0.04	0.8	16	13	59	76	0.01	4	0.4	4.3	247	0.01
KL36-05	521.5	524.5	0.401	4010	0.03	1.2	62	42	180	35	0.01	3	8.6	4.1	132	0.01
KL36-05	524.5	527.5	0.462	4620	0.04	0.9	17	15	400	118	0.01	2	3.2	3.5	200	0.01
KL36-05	527.5	530.5	0.64	6400	0.25	1.6	70	51	10	126	0.01	4	0.4	3.8	220	0.01
KL36-05	530.5	533.5	0.82	8200	0.1	1.7	30	17	12	28	0.01	5	0.3	6.5	210	0.01
KL36-05	533.5	536.5	0.81	8100	0.19	1.4	35	18	15	31	0.01	6	0.9	6.5	67	0.01
KL36-05	536.5	539.5	0.66	6600	0.18	1.1	30	22	2	52	0.01	9	0.01	4.8	132	0.01
KL36-05	539.5	542.5	0.61	6100	0.07	1	25	18	42	43	0.01	5	0.01	3.8	187	0.1
KL36-05	542.5	545.5	0.58	5800	0.07	2.2	37	1470	1070	104	1	6	5.3	5.0	110	0.1
KL36-05	545.5	548.5	0.67	6700	0.12	3.2	1150	1610	560	90	3	5	3.8	4.8	105	0.28
KL36-05	548.5	551.5	0.332	3320	0.14	4.5	151	200	240	106	16	6	55	11.8	36	0.37
KL36-05	551.5	554.5	0.515	5150	0.15	0.7	30	16	14	78	0.01	4	0.5	4.3	74	0.01
KL36-05	554.5	557.5	0.418	4180	0.04	0.7	25	13	49	57	0.01	3	1.7	4.0	191	0.01
KL36-05	557.5	560.5	0.64	6400	0.15	1	60	31	1	45	0.01	6	0.2	3.8	175	0.01
KL36-05	560.5	563.6	0.49	4900	0.07	0.8	48	28	12	71	0.01	5	0.2	4.0	155	0.01
KL36-05	563.6	566.5	0.503	5030	0.16	1	24	22	4	103	0.01	6	0.01	5.0	112	0.01
KL36-05	566.5	569.5	0.389	3890	0.1	1	35	19	2	62	0.01	5	0.01	3.7	133	0.01
KL36-05	569.5	572.5	0.57	5700	0.21	1.4	28	28	2	44	0.01	6	0.01	3.3	130	0.01
KL36-05	572.5	574.1	0.355	3550	0.1	0.1	68	264	170	37	0.01	5	3.3	3.0	212	0.01
KL36-05	574.1	576	0.395	3950	0.09	0.9	32	37	120	60	0.01	3	1	3.5	147	0.01
KL36-05	576	576.8	0.377	3770	0.11	1.2	41	29	5	46	1	7	0.01	3.3	55	0.01
KL36-05	576.8	578.5	0.338	3380	0.11	1	21	16	2	54	1	6	0.01	4.0	147	0.01
KL36-05	578.5	581.5	0.32	3200	0.11	0.6	38	21	3	48	1	5	0.5	3.5	178	0.01
KL36-05	581.5	584.5	0.25	2500	0.04	0.9	22	12	14	24	1	5	0.6	3.7	143	0.01
KL36-05	584.5	587.5	0.368	3680	0.06	0.9	80	32	130	56	1	7	2.9	5.0	171	0.01
KL36-05	587.5	589.5	0.274	2740	0.04	0.1	17	7	6	73	0.01	6	0.01	5.0	187	0.01
KL36-05	589.5	592.6	0.24	2400	0.04	0.1	16	14	90	94	0.01	4	1.2	3.5	220	0.01
KL36-05	592.6	595.2	0.26	2600	0.04	0.1	21	27	240	40	0.01	3	1.2	3.5	201	0.01
KL36-05	595.2	596.5	0.22	2200	0.02	0.1	17	12	24	35	0.01	2	0.5	3.1	252	0.01
KL36-05	596.5	599.5	0.23	2300	0.05	0.7	22	21	150	36	0.01	3	0.8	4.3	157	0.01
KL36-05	599.5	601.5	0.21	2100	0.03	0.1	110	42	560	23	0.01	2	2.5	7.3	122	0.01
KL36-05	601.5	602.7	0.21	2100	0.03	1	118	45	750	41	1	3	3.5	3.3	125	0.01
KL36-05	602.7	604.5	0.2	2000	0.04	1	72	61	580	153	2	2	4.3	4.8	94	0.01
KL36-05	604.5	607.5	0.2	2000	0.04	0.8	56	58	620	69	3	4	2.9	5.8	119	0.01
KL36-05	607.5	609.8	0.33	3300	0.04	1.2	147	113	140	23	2	7	0.6	5.3	105	0.1
KL36-05	609.8	611.5	0.183	1830	0.03	0.1	56	36	16	69	1	5	0.2	3.8	145	0.01
KL36-05	611.5	614.5	0.21	2100	0.03	0.9	58	68	17	48	2	4	1.6	4.1	117	0.01
KL36-05	614.5	617.5	0.2	2000	0.01	0.1	15	14	4	36	1	4	0.01	3.8	150	0.01
KL36-05	617.5	620.5	0.25	2500	0.01	0.1	26	14	1	41	1	4	0.01	5.8	156	0.01
KL36-05	620.5	623.5	0.242	2420	0.01	0.1	218	126	3	57	0.01	3	0.01	3.0	57	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL36-05	623.5	626.5	0.23	2300	0.02	0.1	14	9	7	84	1	5	0.01	4.5	130	0.01
KL36-05	626.5	629.5	0.517	5170	0.05	0.9	31	20	8	40	0.01	10	0.4	5.8	164	0.1
KL36-05	629.5	632.5	0.3	3000	0.04	1.2	201	94	220	40	1	7	2.2	4.5	188	0.12
KL36-05	632.5	635.5	0.25	2500	0.04	0.7	25	15	160	47	0.01	6	0.4	4.0	170	0.01
KL36-05	635.5	638.5	0.291	2910	0.02	0.1	25	20	2	87	0.01	3	0.01	3.5	201	0.01
KL36-05	638.5	641.5	0.159	1590	0.03	0.1	49	21	11	55	0.01	5	0.01	3.8	230	0.01
KL36-05	641.5	644.5	0.132	1320	0.03	0.9	303	193	15	56	1	7	0.6	4.8	124	0.01
KL36-05	644.5	647.5	0.127	1270	0.02	0.1	138	97	14	78	0.01	7	0.3	4.5	175	0.01
KL36-05	647.5	650.5	0.111	1110	0.02	0.1	128	132	150	51	1	4	2.4	4.0	165	0.01
KL36-05	650.5	653.5	0.171	1710	0.03	0.1	73	61	120	43	1	9	2.5	7.8	29	0.01
KL36-05	653.5	656.5	0.099	990	0.03	0.1	13	12	9	32	0.01	6	0.3	5.3	140	0.01
KL36-05	656.5	659.5	0.131	1310	0.02	0.1	17	10	7	57	0.01	5	0.01	3.8	272	0.01
KL36-05	659.5	662.5	0.102	1020	0.02	0.1	52	34	8	43	0.01	5	1	3.3	235	0.01
KL36-05	662.5	665.5	0.12	1200	0.04	0.8	94	66	14	37	1	23	0.9	11.8	135	0.01
KL36-05	665.5	668.5	0.096	960	0.04	0.1	157	93	12	28	1	9	1.3	7.3	190	0.01
KL36-05	668.5	671.5	0.102	1020	0.03	0.1	111	47	10	30	1	8	0.9	4.9	137	0.1
KL36-05	671.5	674.5	0.121	1210	0.01	0.1	131	61	10	36	0.01	12	0.6	4.8	256	0.01
KL36-05	674.5	677.5	0.168	1680	0.03	0.6	192	64	19	135	1	13	3.2	6.3	149	0.01
KL36-05	677.5	680.5	0.192	1920	0.02	0.1	73	53	9	57	1	6	0.6	5.3	191	0.01
KL36-05	680.5	683.5	0.281	2810	0.07	1	136	109	110	53	1	7	36	5.0	109	0.01
KL36-05	683.5	686.5	0.172	1720	0.05	0.1	69	32	9	66	0.01	4	0.6	2.5	231	0.01
KL36-05	686.5	689.5	0.069	690	0.04	0.1	70	22	12	72	1	3	1.6	3.5	261	0.01
KL36-05	689.5	692.5	0.108	1080	0.03	0.1	41	32	28	98	0.01	1	1.7	2.3	205	0.01
KL36-05	692.5	695.5	0.053	530	0.02	0.1	19	21	8	50	0.01	6	1.2	3.5	183	0.01
KL36-05	695.5	698.5	0.0291	291	0.08	0.1	27	24	28	96	0.01	16	1.5	3.5	340	0.01
KL36-05	698.5	701.2	0.0369	369	0.03	0.1	17	27	33	46	0.01	6	1	2.5	163	0.01
KL36-05	701.2	704.2	0.115	1150	0.05	0.1	28	21	160	50	1	3	34	3.3	248	0.01
KL36-05	704.2	707.5	0.08	800	0.17	0.7	33	40	55	84	1	7	12.9	7.3	231	0.01
KL36-05	707.5	710.5	0.171	1710	0.03	0.1	17	53	12	50	0.01	6	1.7	3.3	225	0.01
KL36-05	710.5	713.3	0.112	1120	0.03	0.1	20	34	16	88	1	7	2.2	4.0	317	0.01
KL36-05	713.3	716.5	0.043	430	0.02	0.1	77	31	52	45	1	6	1.1	3.0	260	0.01
KL36-05	716.5	719.5	0.094	940	0.04	0.1	41	50	9	84	1	6	1.2	3.0	167	0.01
KL36-05	719.5	722.5	0.12	1200	0.02	0.1	14	21	5	60	0.01	4	0.3	3.5	160	0.01
KL36-05	722.5	725.5	0.199	1990	0.02	0.1	23	29	3	56	0.01	7	0.4	4.5	164	0.01
KL36-05	725.5	728.5	0.146	1460	0.03	0.1	91	54	120	478	1	7	1.5	4.8	260	0.01
KL36-05	728.5	731.5	0.088	880	0.01	0.1	117	17	4	150	0.01	5	0.3	3.0	190	0.01
KL36-05	731.5	734.5	0.193	1930	0.02	0.7	16	12	3	31	0.01	4	0.6	3.3	143	0.01
KL36-05	734.5	737	0.22	2200	0.06	0.1	27	18	8	65	1	6	0.6	5.0	187	0.01
KL36-05	737	740	0.117	1170	0.04	0.1	14	14	19	30	1	5	0.4	3.3	191	0.01
KL36-05	740	742.7	0.168	1680	0.03	1	33	25	5	44	1	6	1.2	5.0	242	0.01
KL36-05	742.7	745.7	0.081	810	0.01	0.1	25	13	3	45	0.01	9	0.2	3.0	213	0.01
KL36-05	745.7	748.7	0.313	3130	0.06	1.6	22	42	65	70	9	10	1.8	5.5	137	0.01
KL36-05	748.7	751.8	0.23	2300	0.05	1	52	55	66	101	3	3	1.1	4.5	219	0.01
KL36-05	751.8	754.8	0.24	2400	0.06	1.1	32	49	19	116	0.01	11	1.2	9.6	170	0.01
KL36-05	754.8	757.5	0.22	2200	0.08	1.3	22	30	100	82	4	6	6.1	5.5	124	0.01
KL36-05	757.5	760.3	0.202	2020	0.08	0.6	46	51	200	51	1	5	2.6	4.9	105	0.01
KL36-05	760.3	763.4	0.107	1070	0.08	0.7	28	36	15	52	2	5	3.7	4.3	115	0.01
KL36-05	763.4	766.5	0.084	840	0.07	0.1	33	38	67	192	1	7	1.6	3.8	232	0.01
KL36-05	766.5	769.5	0.0315	315	0.03	0.1	23	31	7	65	0.01	4	1.3	2.0	223	0.01
KL36-05	769.5	772.3	0.0191	191	0.03	0.1	28	23	14	64	0.01	4	1.4	1.4	141	0.01
KL36-05	772.3	774.4	0.023	230	0.07	0.1	23	25	16	57	0.01	5	1.4	1.8	222	0.01
KL36-05	774.4	776.5	0.0197	197	0.02	0.1	34	58	13	55	0.01	7	2	3.3	136	0.01
KL36-05	776.5	779.5	0.065	650	0.09	0.1	62	37	15	127	1	8	3.1	4.4	262	0.01
KL36-05	779.5	781.5	0.0149	149	0.22	0.1	70	85	17	46	2	21	3.6	4.9	205	0.01
KL36-06	0	2.5	0.0125	125	0.04	0.1	169	76	11	3	0.01	1	0.5	1.2	15	0.01
KL36-06	2.5	5.5	0.0205	205	0.07	0.1	309	146	7	2	0.01	1	0.5	2.2	16	0.01
KL36-06	5.5	8.5	0.0114	114	0.06	0.1	226	97	7	5	0.01	1	0.4	1.7	15	0.01
KL36-06	8.5	11.5	0.094	940	0.05	0.7	219	101	10	4	2	1	0.9	1.9	14	0.01
KL36-06	11.5	14.5	0.0062	62	0.03	0.1	520	208	9	3	0.01	1	0.6	2.2	15	0.01
KL36-06	14.5	17.5	0.0041	41	0.03	0.1	430	195	6	2	0.01	1	0.3	1.7	16	0.01
KL36-06	17.5	20.5	0.0162	162	0.04	3.1	2210	2000	18	4	0.01	1	24	4.2	16	0.1
KL36-06	20.5	23.5	0.0024	24	0.02	1	397	269	8	3	0.01	1	1	1.5	13	0.01
KL36-06	23.5	26.5	0.006	60	0.04	1	790	380	10	4	0.01	1	1.9	2.4	14	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL36-06	26.5	29.5	0.0078		78	0.02	0.1	398	340	9	3	0.01	1	1.4	1.2	12	0.01
KL36-06	29.5	32.5	0.0036		36	0.04	0.7	500	172	15	1	0.01	1	1.2	2.4	15	0.01
KL36-06	32.5	35.5	0.0035		35	0.01	0.1	229	106	8	4	0.01	1	0.6	1.5	13	0.01
KL36-06	35.5	38.5	0.0115		115	0.01	0.1	134	68	11	3	0.01	1	0.7	1.3	15	0.01
KL36-06	38.5	41.5	0.0088		88	0.01	0.1	130	54	8	3	0.01	1	0.8	2.1	16	0.01
KL36-06	41.5	44.5	0.0119		119	0.01	0.1	71	33	8	4	0.01	1	0.3	1.3	22	0.01
KL36-06	44.5	47.5	0.0083		83	0.01	0.1	50	25	6	2	0.01	1	0.2	0.5	25	0.01
KL36-06	47.5	50.5	0.0038		38	0.01	0.1	122	52	8	1	0.01	1	0.5	1.1	23	0.01
KL36-06	50.5	53.5	0.0032		32	0.01	0.1	164	88	6	1	0.01	1	0.4	0.7	16	0.01
KL36-06	53.5	56.5	0.003		30	0.01	0.1	377	87	9	2	0.01	1	0.8	1.3	14	0.01
KL36-06	56.5	59.5	0.0027		27	0.02	0.1	660	187	10	2	0.01	1	1.2	0.9	19	0.01
KL36-06	59.5	62.5	0.0029		29	0.01	0.1	189	78	9	1	0.01	1	0.6	0.7	15	0.01
KL36-06	62.5	65.5	0.0027		27	0.21	1.6	670	299	16	2	0.01	1	2.4	2.2	15	0.17
KL36-06	65.5	68.5	0.0017		17	0.02	0.1	315	141	11	2	0.01	1	0.5	1.5	17	0.01
KL36-06	68.5	71.5	0.0066		66	0.01	0.1	62	31	9	4	0.01	1	0.2	1.2	21	0.01
KL36-06	71.5	74.5	0.0021		21	0.01	0.1	150	84	10	3	0.01	1	0.01	1.3	16	0.01
KL36-06	74.5	77.5	0.0035		35	0.01	0.1	23	17	11	4	0.01	1	0.3	1.4	23	0.01
KL36-06	77.5	80.5	0.0029		29	0.01	0.1	26	17	14	2	0.01	1	0.2	1.2	19	0.01
KL36-06	80.5	83.5	0.0024		24	0.01	0.1	34	30	14	3	0.01	1	0.2	1.1	21	0.01
KL36-06	83.5	86.5	0.0065		65	0.06	35	3000	11800	62	2	0.01	1	30	1.9	33	0.01
KL36-06	86.5	89.5	0.0075		75	0.01	0.6	121	111	15	4	0.01	1	0.5	0.6	29	0.01
KL36-06	89.5	92.5	0.017		170	0.1	9.5	7970	5070	33	3	0.01	1	8	3.3	24	0.01
KL36-06	92.5	95.5	0.0072		72	0.27	1.5	3180	1700	330	4	0.01	1	78	4.3	32	0.89
KL36-06	95.5	98.5	0.0045		45	0.01	0.1	42	47	11	6	0.01	1	0.7	1.7	18	0.01
KL36-06	98.5	101.5	0.0052		52	0.01	0.1	51	47	20	5	0.01	1	0.6	1.4	30	0.01
KL36-06	101.5	104.5	0.005		50	0.03	1	560	257	14	5	0.01	1	1.2	2.1	33	0.01
KL36-06	104.5	107.5	0.0118		118	0.02	1.4	640	510	12	3	0.01	1	0.8	1.7	14	0.01
KL36-06	107.5	110.5	0.0052		52	0.02	0.1	126	122	6	2	0.01	1	0.3	0.7	13	0.01
KL36-06	110.5	113.5	0.0048		48	0.02	0.1	231	216	9	3	0.01	1	0.4	1.1	16	0.01
KL36-06	113.5	116.5	0.0038		38	0.01	0.9	460	590	17	1	0.01	1	1.4	2.1	30	0.01
KL36-06	116.5	119.5	0.046		460	0.02	0.7	334	430	22	5	0.01	2	0.7	2.7	32	0.01
KL36-06	119.5	122.5	0.0045		45	0.01	0.1	115	168	33	6	0.01	2	0.6	2.3	70	0.01
KL36-06	122.5	125.5	0.0234		234	0.17	40	7100	13400	34	19	78	2	4.6	33.7	32	0.1
KL36-06	125.5	128.5	0.0044		44	0.01	1	480	670	18	3	1	1	0.8	4.4	19	0.01
KL36-06	128.5	131.5	0.0359		359	0.01	0.9	560	610	22	6	1	1	0.8	6.9	30	0.01
KL36-06	131.5	134.5	0.004		40	0.01	0.8	140	470	29	5	1	3	0.4	1.5	28	0.01
KL36-06	134.5	137.5	0.0029		29	0.01	0.7	194	338	24	21	1	2	0.3	1.2	30	0.01
KL36-06	137.5	140.5	0.0052		52	0.01	1.8	67	264	23	7	4	2	0.01	2.0	28	0.01
KL36-06	140.5	143.5	0.0034		34	0.01	0.1	86	160	18	9	0.01	1	0.3	1.1	25	0.01
KL36-06	143.5	146.5	0.0037		37	0.01	0.1	132	185	20	8	0.01	1	0.4	1.8	24	0.01
KL36-06	146.5	149.5	0.005		50	0.01	0.1	281	640	28	20	0.01	1	0.7	3.1	21	0.01
KL36-06	149.5	152.5	0.0047		47	0.01	2.3	238	610	27	27	6	1	1.2	4.4	19	0.01
KL36-06	152.5	155.5	0.0115		115	0.02	2.6	5440	1060	25	20	6	2	1.5	12.2	21	0.01
KL36-06	155.5	158.5	0.0074		74	0.01	1.4	215	275	16	10	5	1	1.6	11.7	18	0.01
KL36-06	158.5	161.5	0.007		70	0.02	10.2	620	890	18	29	32	3	2.1	54.0	22	0.01
KL36-06	161.5	164.5	0.0061		61	0.02	4.5	740	1120	56	24	19	1	1.1	5.1	24	0.01
KL36-06	164.5	167.5	0.0082		82	0.03	0.8	970	285	54	56	19	1	5.2	4.0	26	0.01
KL36-06	167.5	170.5	0.0017		17	0.01	0.1	52	84	9	5	0.01	1	0.3	1.8	15	0.01
KL36-06	170.5	173.5	0.0056		56	0.04	0.1	194	198	23	6	1	1	0.6	1.4	15	0.01
KL36-06	173.5	176.5	0.005		50	0.07	0.9	249	180	47	10	4	1	1	2.3	18	0.01
KL36-06	176.5	179.5	0.0035		35	0.03	0.9	166	183	32	8	20	1	1.3	3.0	19	0.01
KL36-06	179.5	182.5	0.0037		37	0.01	1	153	149	26	6	16	1	1	2.6	20	0.01
KL36-06	182.5	185.5	0.076		760	0.02	2.8	1150	181	120	11	28	5	2.9	6.1	27	0.01
KL36-06	185.5	188	0.0045		45	0.02	0.7	106	88	27	9	8	1	1.8	2.0	21	0.01
KL36-06	188	191.1	0.0044		44	0.04	1	269	610	39	8	2	1	1.2	3.4	26	0.01
KL36-06	191.1	193.7	0.0033		33	0.01	0.7	338	730	28	2	4	1	0.6	1.4	19	0.01
KL36-06	193.7	196.7	0.0062		62	0.02	1.6	930	670	43	12	8	1	1	5.0	21	0.01
KL36-06	196.7	199.8	0.198		1980	0.03	2.2	1770	710	32	8	10	11	0.7	5.7	33	0.01
KL36-06	199.8	202.9	0.62		6200	0.21	5.2	790	383	51	10	3	18	1.6	4.4	44	0.01
KL36-06	202.9	206	0.112		1120	0.05	0.8	197	120	18	103	1	4	1	2.1	49	0.01
KL36-06	206	207.9	0.07		700	0.03	0.7	117	61	11	23	2	4	1	1.5	70	0.01
KL36-06	207.9	210	0.081		810	0.03	0.9	118	152	16	18	1	3	0.9	1.4	56	0.01
KL36-06	210	212.3	0.061		610	0.05	0.6	359	107	14	33	1	3	1.2	1.9	91	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL36-06	212.3	215.4	0.0383	383	0.04	0.6	244	250	9	34	1	1	3.3	1.0	95	0.01
KL36-06	215.4	216.9	0.121	1210	0.04	1.1	146	147	7	110	0.01	4	0.4	3.2	32	0.01
KL36-06	216.9	218.5	2.2	22000	0.32	19.4	158	112	20	345	9	4	2.3	3.6	148	0.19
KL36-06	218.5	221.5	0.72	7200	0.23	15	200	245	100	63	6	8	13.6	9.6	81	0.1
KL36-06	221.5	223.9	0.96	9600	0.48	28.9	170	322	72	560	58	11	13.3	18.4	87	0.1
KL36-06	223.9	227	1.15	11500	0.33	21.9	810	970	83	245	16	8	10.8	6.0	73	0.16
KL36-06	227	229	0.141	1410	0.09	3.3	218	249	29	67	4	12	6.9	2.9	68	0.01
KL36-06	229	230.9	0.22	2200	0.11	3.2	119	272	18	44	5	8	3.1	4.6	43	0.01
KL36-06	230.9	234	0.07	700	0.07	2.4	226	385	13	19	3	7	2.3	5.3	32	0.01
KL36-06	234	236.5	0.0246	246	0.09	1.2	268	340	10	20	2	4	0.7	2.8	18	0.01
KL36-06	236.5	239.5	0.076	760	0.08	1.4	570	322	14	25	2	5	2.4	3.0	97	0.01
KL36-06	239.5	242.5	0.179	1790	0.08	3.1	98	110	16	112	2	11	2.3	4.5	37	0.01
KL36-06	242.5	245	0.205	2050	0.14	3.5	426	450	34	231	5	10	2.7	7.1	38	0.01
KL36-06	245	247.2	0.21	2100	0.16	3.4	990	520	30	219	2	7	7.3	6.0	39	0.01
KL36-06	247.2	250.2	0.185	1850	0.11	2.1	240	210	16	264	2	8	1.8	4.0	115	0.01
KL36-06	250.2	251.5	0.28	2800	0.12	2.9	207	221	19	63	3	9	2.7	4.1	33	0.01
KL36-06	251.5	254.5	0.335	3350	0.12	3.5	580	430	18	38	4	12	4.4	4.7	27	0.01
KL36-06	254.5	256.6	0.204	2040	0.12	2	109	141	18	124	1	5	1.4	2.6	33	0.01
KL36-06	256.6	258.2	0.2	2000	0.12	3.8	96	640	28	19	4	8	3.5	4.2	28	0.01
KL36-06	258.2	260	0.24	2400	0.08	3	127	550	34	65	4	10	1.4	7.1	23	0.01
KL36-06	260	263	0.341	3410	0.07	4.4	83	263	15	300	5	8	2.6	5.9	21	0.01
KL36-06	263	266.2	0.31	3100	0.05	3.3	110	145	10	189	2	9	1.8	6.3	20	0.01
KL36-06	266.2	269.2	0.29	2900	0.07	4.9	402	880	14	124	7	8	2	5.4	19	0.01
KL36-06	269.2	270.4	0.419	4190	0.52	12.4	374	342	120	180	44	11	5	11.1	57	0.01
KL36-06	270.4	273.5	0.78	7800	1.14	27.8	850	660	410	59	139	13	10.1	2.5	60	0.11
KL36-06	273.5	275.5	1.56	15600	1	18.3	151	149	56	365	48	27	8	16.5	127	0.3
KL36-06	275.5	278.5	1.03	10300	0.5	10.1	184	164	100	29	32	15	24	40.0	93	0.14
KL36-06	278.5	281.5	2.35	23500	0.6	17	190	339	80	20	24	10	19	41.8	130	0.22
KL36-06	281.5	283.7	2.57	25700	0.62	14.5	100	124	70	13	8	5	22	37.5	56	0.22
KL36-06	283.7	285.6	1.93	19300	0.86	13.2	104	136	50	31	6	3	17	30.0	99	0.1
KL36-06	285.6	287.5	7.25	72500	1.38	23.4	287	490	70	8	64	7	36	37.5	43	0.11
KL36-06	287.5	290.5	1.52	15200	0.69	18.5	186	380	70	5	33	2	17.7	57.0	23	0.1
KL36-06	290.5	293.5	2.56	25600	1.43	42	440	650	100	15	100	4	32	68.0	30	0.23
KL36-06	293.5	295.7	0.57	5700	1.39	16.5	620	1460	27	79	38	6	2.3	10.6	24	0.1
KL36-06	295.7	297	10.8	108000	5.8	39	241	175	130	88	97	52	75	20.0	92	0.26
KL36-06	297	299.5	18.2	182000	2.77	49	168	95	600	11	86	1	435	20.0	48	0.65
KL36-06	299.5	302.5	11	110000	2.71	70	121	67	83	15	49	1	95	15.0	90	0.76
KL36-06	302.5	305.5	2.88	28800	0.97	16.4	131	142	50	30	56	20	5.3	9.0	74	0.14
KL36-06	305.5	308.5	0.364	3640	0.2	8.4	3370	2150	33	6	8	1	6.2	7.0	23	0.1
KL36-06	308.5	311.5	0.34	3400	0.18	2.5	1340	510	60	15	3	1	3.9	4.0	25	0.01
KL36-06	311.5	314.5	0.553	5530	0.26	12.5	7400	2780	44	31	12	7	6.5	7.3	31	0.1
KL36-06	314.5	317.5	0.751	7510	1.04	34.7	46000	16500	1160	28	24	7	22	16.0	85	4.32
KL36-06	317.5	320.1	6.5	65000	1.32	103	8270	2900	500	11	86	60	60	27.5	110	1.48
KL36-06	320.1	322.5	2.89	28900	0.91	63	18000	7700	710	37	72	65	30	18.0	71	2.1
KL36-06	322.5	325.5	1.47	14700	0.91	9.7	2550	570	68	14	7	21	6.9	10.5	41	0.13
KL36-06	325.5	328.4	1.84	18400	1.76	5	850	320	79	22	7	17	4.4	13.5	56	0.01
KL36-06	328.4	330.6	1.31	13100	0.72	12	3730	980	48	240	68	46	3.9	15.0	27	0.01
KL36-06	330.6	332.5	1.01	10100	0.6	11.2	1810	1570	47	180	38	37	4.6	16.5	59	0.01
KL36-06	332.5	335.5	2.43	24300	0.56	3.7	950	240	460	58	6	16	22	61.0	100	1.43
KL36-06	335.5	338.5	1.39	13900	0.6	2.5	3780	2890	710	271	4	35	9.9	63.5	45	6.62
KL36-06	338.5	341.5	6.35	63500	0.86	5.2	1480	1390	560	108	4	29	8.2	25.0	101	2.4
KL36-06	341.5	344.4	0.61	6100	0.23	3.2	8200	600	43	64	4	66	5	4.3	28	0.01
KL36-06	344.4	347.5	0.45	4500	0.23	2.1	5100	159	35	49	3	60	3.1	8.8	18	0.01
KL36-06	347.5	349.5	1.41	14100	0.57	3	1220	67	23	271	3	35	1.9	8.5	19	0.01
KL36-06	349.5	352.5	1.73	17300	0.59	3.4	1350	103	16	242	3	48	2.9	10.5	26	0.01
KL36-06	352.5	353.5	1.27	12700	0.39	3.1	1050	175	20	498	2	42	2.3	7.5	21	0.01
KL36-06	353.5	356.5	0.63	6300	0.34	2	970	81	26	90	1	43	2.4	6.8	54	0.01
KL36-06	356.5	359.5	0.58	5800	0.2	2.4	425	73	20	59	2	22	3.4	4.5	16	0.01
KL36-06	359.5	362.5	0.66	6600	0.23	2	660	165	24	188	1	30	1.6	4.0	20	0.01
KL36-06	362.5	365.5	0.57	5700	0.39	2.5	820	34	25	25	7	45	2	6.3	18	0.01
KL36-06	365.5	368.5	0.513	5130	0.38	3.4	1840	236	26	82	19	18	3.7	8.5	20	0.01
KL36-06	368.5	371.5	0.3	3000	0.11	1.5	317	65	14	134	2	3	1.6	4.2	29	0.01
KL36-06	371.5	374.5	0.32	3200	0.21	2	415	175	6	46	3	6	0.7	11.3	30	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL36-06	374.5	377.5	1.25	12500	1.86	9.1	1340	56	12	8	24	15	1.1	19.0	31	0.01
KL36-06	377.5	380.5	2	20000	2.47	5	190	57	10	14	3	31	0.7	15.0	41	0.2
KL36-06	380.5	383	2.22	22200	2	3.5	106	20	2	7	2	31	0.01	26.0	26	0.01
KL36-06	383	386	1.74	17400	1.28	4.1	164	145	12	16	3	33	1.8	23.0	42	0.01
KL36-06	386	389	4.12	41200	1.74	7.8	341	39	3	275	3	48	1.3	26.5	26	0.01
KL36-06	389	392	3.2	32000	1.46	5.7	331	20	0.01	20	3	64	0.9	18.0	27	0.01
KL36-06	392	395	2.26	22600	0.89	5.3	412	36	3	12	3	46	1.6	8.7	41	0.01
KL36-06	395	397.7	0.76	7600	0.65	2.2	359	27	6	8	4	76	1.8	10.3	47	0.01
KL36-06	397.7	400.5	2.59	25900	1.96	6.2	710	17	8	9	8	79	1.8	20.0	42	0.01
KL36-06	400.5	402.8	0.99	9900	1.16	2.2	117	47	4	64	1	32	0.4	12.9	99	0.01
KL36-06	402.8	404.5	0.52	5200	0.54	1.3	198	30	5	181	0.01	38	0.3	7.3	60	0.01
KL36-06	404.5	407.5	2.32	23200	2.48	5.2	193	22	0.01	11	2	40	1	43.5	37	0.01
KL36-06	407.5	410.5	1.26	12600	2.47	2.2	112	21	0.01	5	1	37	0.01	22.0	46	0.01
KL36-06	410.5	413.5	3.83	38300	5.55	7.8	301	30	0.01	8	1	65	0.01	25.0	39	0.01
KL36-06	413.5	416.5	3	30000	3.68	9.9	241	46	0.01	5	5	47	1.6	34.0	54	0.01
KL36-06	416.5	419.5	4.55	45500	3.48	11.8	800	87	0.01	11	0.01	70	0.3	18.0	64	0.01
KL36-06	419.5	422.5	5.31	53100	2.96	14.2	235	73	5	1260	4	37	1.1	37.5	97	0.01
KL36-06	422.5	424.2	3.56	35600	1.31	11.4	114	35	5	279	3	26	0.8	22.0	84	0.01
KL36-06	424.2	426	1.73	17300	0.51	5.1	55	20	4	690	3	12	0.4	9.8	96	0.01
KL36-06	426	427.8	1.25	12500	0.53	3	62	21	4	88	2	13	0.6	8.5	125	0.01
KL36-06	427.8	429.5	0.8	8000	0.52	1.8	65	12	3	60	0.01	8	0.01	5.0	133	0.01
KL36-06	429.5	431	0.855	8550	0.2	2.1	35	10	3	102	1	7	0.01	4.8	125	0.01
KL36-06	431	434	0.94	9400	0.51	2	69	11	3	100	1	10	0.01	5.0	147	0.01
KL36-06	434	436.9	1.13	11300	0.52	3.8	47	21	3	440	6	15	0.8	13.5	88	0.01
KL36-06	436.9	439.5	0.93	9300	1.11	2.3	74	13	0.01	35	1	9	0.3	5.8	100	0.01
KL36-06	439.5	441.4	2.48	24800	0.74	6.2	44	8	0.01	45	4	7	0.5	3.8	24	0.01
KL36-06	441.4	443.5	1.02	10200	0.5	3.6	31	8	0.01	67	2	5	0.5	3.5	119	0.01
KL36-06	443.5	446.5	1.01	10100	0.65	3.1	64	25	0.01	54	1	5	0.3	6.5	116	0.01
KL36-06	446.5	449.5	0.45	4500	0.42	2.1	88	17	0.01	48	2	6	0.3	3.5	129	0.01
KL36-06	449.5	452.5	0.37	3700	0.24	1.2	63	30	0.01	92	2	3	0.6	3.3	147	0.01
KL36-06	452.5	455.5	0.26	2600	0.15	1.2	197	75	0.01	64	1	4	0.4	3.0	175	0.01
KL36-06	455.5	458.5	0.32	3200	0.19	1.7	370	85	0.01	75	2	5	0.4	4.0	131	0.01
KL36-06	458.5	461.5	0.24	2400	0.08	0.9	87	41	0.01	40	0.01	4	0.2	1.8	142	0.01
KL36-06	461.5	464.5	0.183	1830	0.06	0.9	550	143	0.01	46	0.01	3	0.4	2.3	162	0.01
KL36-06	464.5	467.5	0.5	5000	0.1	1	74	27	0.01	55	1	4	1.2	4.5	203	0.01
KL36-06	467.5	470.5	0.34	3400	0.18	1.3	76	27	0.01	29	2	5	0.4	2.5	135	0.01
KL36-06	470.5	473.5	0.29	2900	0.15	1.2	305	111	0.01	89	1	4	1.2	3.0	146	0.01
KL36-06	473.5	476.5	0.25	2500	0.05	1	95	45	0.01	11	0.01	6	0.4	2.3	176	0.01
KL36-06	476.5	479.5	1.31	13100	0.55	4.2	251	116	0.01	20	1	3	0.6	1.6	141	0.01
KL36-06	479.5	482.5	0.43	4300	0.1	1.4	34	14	0.01	102	1	4	0.3	4.0	110	0.01
KL36-06	482.5	485.5	0.26	2600	0.1	0.9	49	14	0.01	35	1	5	0.3	2.6	119	0.01
KL36-06	485.5	488.5	0.12	1200	0.05	0.9	76	14	0.01	23	1	4	0.6	1.2	143	0.01
KL36-06	488.5	491.5	0.178	1780	0.06	1	120	27	0.01	38	1	5	0.01	2.0	157	0.01
KL36-06	491.5	494.5	0.17	1700	0.03	0.7	39	12	0.01	36	0.01	4	0.01	1.5	166	0.01
KL36-06	494.5	497.5	1.02	10200	0.57	2.6	30	14	5	103	1	10	0.01	6.9	118	0.01
KL36-06	497.5	500.5	0.183	1830	0.11	0.6	29	10	0.01	53	0.01	4	0.2	2.5	143	0.01
KL36-06	500.5	503.5	1.04	10400	0.69	2.5	71	30	0.01	73	1	9	0.2	7.5	89	0.01
KL36-06	503.5	506.5	0.25	2500	0.14	1.7	210	100	0.01	45	3	4	0.2	3.5	148	0.01
KL36-06	506.5	509.5	0.36	3600	0.2	2	332	125	58	123	2	16	7.2	5.5	127	0.01
KL36-06	509.5	512.5	0.25	2500	0.09	0.9	105	46	19	32	1	4	3.8	3.0	126	0.01
KL36-06	512.5	514	0.37	3700	0.06	0.8	38	21	0.01	17	0.01	3	0.4	4.3	216	0.01
KL36-06	514	516.5	0.21	2100	0.02	0.5	44	20	0.01	22	0.01	3	0.01	1.8	153	0.01
KL36-06	516.5	518.5	0.25	2500	0.05	0.7	192	83	0.01	30	0.01	6	0.4	2.8	122	0.01
KL36-06	518.5	521.5	0.25	2500	0.04	0.7	48	21	0.01	26	0.01	4	0.01	3.0	157	0.01
KL36-06	521.5	524.5	0.44	4400	0.1	1.1	132	48	10	50	0.01	2	0.8	3.5	137	0.01
KL36-06	524.5	527.5	0.61	6100	0.14	1.5	194	58	34	73	1	6	6.5	6.0	160	0.01
KL36-06	527.5	530.5	0.33	3300	0.08	0.9	59	24	3	74	0.01	9	0.4	4.0	179	0.01
KL36-06	530.5	533.5	0.3	3000	0.05	0.6	41	13	4	46	0.01	6	0.01	3.5	183	0.01
KL36-06	533.5	535.3	0.3	3000	0.05	0.6	62	24	22	63	1	3	3.9	3.3	176	0.01
KL36-06	535.3	537.2	0.28	2800	0.04	0.7	39	16	3	45	0.01	2	0.01	3.2	231	0.01
KL36-06	537.2	539.5	0.25	2500	0.02	0.6	41	19	0.01	34	0.01	3	0.5	3.0	230	0.01
KL36-06	539.5	542.5	0.174	1740	0.04	0.8	46	20	16	68	0.01	4	0.8	3.8	219	0.01
KL36-06	542.5	545.5	0.145	1450	0.13	5	2780	182	398	40	1	9	3.6	2.3	283	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL36-06	545.5	548.5	0.026		260	0.02	0.1	45	16	5	22	0.01	8	0.6	4.0	293	0.01
KL36-06	548.5	551.5	0.25		2500	0.26	0.7	93	12	7	38	0.01	10	0.5	5.4	196	0.01
KL36-06	551.5	554.5	0.052		520	0.01	0.1	48	7	9	1070	0.01	8	0.4	6.0	69	0.01
KL36-06	554.5	557.5	0.056		560	0.01	0.1	11	8	10	56	0.01	6	1.1	2.0	75	0.01
KL36-06	557.5	560.5	0.0247		247	0.04	0.1	150	30	14	59	1	6	0.5	0.8	263	0.01
KL36-06	560.5	563.5	0.064		640	0.04	0.1	310	40	22	63	0.01	2	0.5	1.3	304	0.01
KL36-06	563.5	566.5	0.126		1260	0.12	0.9	580	54	11	65	1	5	0.9	3.0	228	0.01
KL36-06	566.5	569.5	0.18		1800	0.07	0.1	40	10	0.01	31	0.01	2	0.01	2.5	190	0.01
KL36-06	569.5	572.5	0.163		1630	0.07	0.5	15	5	0.01	41	1	5	0.01	2.5	168	0.01
KL36-06	572.5	575.5	0.135		1350	0.05	0.5	80	24	8	38	1	6	0.7	2.5	24	0.01
KL36-06	575.5	578.5	0.063		630	0.02	0.6	151	50	9	45	1	5	0.5	2.0	36	0.01
KL36-06	578.5	581.5	0.062		620	0.03	0.1	61	43	32	42	1	6	1.2	1.8	192	0.01
KL36-06	581.5	584.5	0.061		610	0.04	0.5	101	36	18	58	1	3	1.4	1.0	216	0.01
KL36-06	584.5	587.5	0.045		450	0.04	0.1	74	29	5	188	0.01	3	0.4	1.5	203	0.01
KL36-06	587.5	590.5	0.046		460	0.02	0.1	47	23	19	33	0.01	2	0.6	0.8	150	0.01
KL36-06	590.5	593.5	0.103		1030	0.03	0.1	78	29	6	22	0.01	2	0.7	0.8	200	0.01
KL36-06	593.5	596.5	0.047		470	0.02	0.1	131	36	3	19	0.01	3	0.3	0.8	199	0.01
KL36-06	596.5	599.5	0.121		1210	0.02	0.7	156	44	25	31	1	2	3.8	1.0	60	0.01
KL36-06	599.5	602.3	0.07		700	0.01	0.1	72	28	21	18	0.01	2	0.9	0.5	44	0.01
KL36-06	602.3	605.3	0.078		780	0.06	0.1	240	40	2	31	0.01	3	0.01	0.8	206	0.01
KL36-06	605.3	608.3	0.107		1070	0.04	0.6	108	57	10	64	0.01	1	2.8	0.8	260	0.01
KL36-06	608.3	610.2	0.137		1370	0.05	0.1	35	17	9	29	0.01	2	1	0.8	163	0.01
KL36-06	610.2	612.7	0.078		780	0.03	0.1	80	26	4	46	0.01	1	0.6	1.1	222	0.01
KL36-06	612.7	614.5	0.047		470	0.01	0.1	47	17	0.01	31	0.01	2	0.4	2.5	216	0.01
KL36-06	614.5	616.8	0.075		750	0.01	0.1	50	18	34	28	0.01	1	1.9	0.8	222	0.01
KL36-06	616.8	619.8	0.081		810	0.02	0.7	43	25	110	29	0.01	2	3.4	1.2	43	0.01
KL36-06	619.8	622.5	0.108		1080	0.01	0.1	51	26	200	23	0.01	2	8.8	1.0	34	0.01
KL36-06	622.5	625.4	0.078		780	0.01	0.1	24	19	180	20	0.01	2	4.8	0.5	24	0.01
KL36-06	625.4	628.5	0.054		540	0.02	0.7	152	105	53	28	1	3	1.5	1.3	28	0.01
KL36-06	628.5	630	0.26		2600	0.11	4.4	114	124	820	29	2	5	17	3.8	44	0.01
KL36-06	630	632.3	0.053		530	0.03	1.2	73	143	120	37	1	4	2.4	2.3	24	0.01
KL36-06	632.3	635.5	0.031		310	0.05	1.7	510	257	56	56	1	7	2.2	3.6	27	0.01
KL36-06	635.5	638.5	0.0246		246	0.02	2	151	144	39	29	5	2	1.3	1.0	27	0.01
KL36-06	638.5	641.5	0.0141		141	0.03	0.1	178	87	32	54	1	3	1.1	1.3	332	0.01
KL36-06	641.5	644.5	0.0108		108	0.02	0.1	304	40	14	26	0.01	4	1.7	0.5	83	0.01
KL36-06	644.5	647.5	0.0064		64	0.05	0.1	144	60	10	13	0.01	7	1.6	2.4	280	0.01
KL36-06	647.5	650.2	0.0053		53	0.05	0.1	45	43	16	16	0.01	6	1.2	1.2	183	0.01
KL36-06	650.2	652.3	0.0228		228	0.07	0.1	78	70	62	31	0.01	2	13.8	0.9	450	0.01
KL36-06	652.3	654.6	0.0062		62	0.03	0.1	53	31	17	15	0.01	2	0.3	0.0	235	0.01
KL36-06	654.6	657.7	0.044		440	0.05	0.1	113	71	160	32	0.01	5	16	1.2	315	0.01
KL36-06	657.7	660.2	0.0053		53	0.01	0.1	73	28	9	37	0.01	3	1.1	0.0	235	0.01
KL36-06	660.2	661.5	0.0065		65	0.01	0.6	106	38	15	30	0.01	4	0.7	0.0	233	0.01
KL36-06	661.5	664.5	0.0068		68	0.01	0.1	133	52	17	24	0.01	3	0.7	0.0	268	0.01
KL36-06	664.5	668	0.0066		66	0.03	0.1	89	46	24	15	0.01	2	1.5	0.7	260	0.01
KL36-06	668	670.7	0.0049		49	0.01	0.1	195	26	9	33	0.01	1	1.2	0.0	262	0.01
KL36-06	670.7	673.8	0.27		2700	0.54	8.7	149	71	930	18	14	5	102	1.1	241	0.01
KL36-06	673.8	676.8	0.069		690	0.04	1.7	80	37	120	20	1	3	10.2	0.8	240	0.01
KL36-06	676.8	678.7	0.0086		86	0.01	0.1	25	15	14	25	0.01	6	0.2	0.0	246	0.01
KL36-06	678.7	680.2	0.0151		151	0.01	0.1	21	19	19	26	0.01	4	0.9	1.2	278	0.01
KL36-06	680.2	682.5	0.0193		193	0.01	0.1	19	11	27	49	0.01	3	0.8	1.3	265	0.01
KL36-06	682.5	685.5	0.0186		186	0.01	0.1	23	8	16	28	0.01	6	1.4	0.5	322	0.01
KL36-06	685.5	687.5	0.0319		319	0.01	0.1	21	7	33	19	0.01	3	3	1.6	303	0.01
KL36-06	687.5	689.5	0.0139		139	0.01	0.1	14	6	8	15	0.01	2	0.7	0.0	268	0.01
KL36-06	689.5	692.5	0.048		480	0.03	0.1	20	9	9	50	0.01	6	0.5	1.3	314	0.01
KL36-06	692.5	695.5	0.043		430	0.01	0.1	17	9	4	23	0.01	5	0.3	1.1	295	0.01
KL36-06	695.5	698.5	0.015		150	0.01	0.1	14	6	8	22	0.01	4	1	0.7	345	0.01
KL36-06	698.5	701.5	0.0134		134	0.01	0.1	17	6	11	131	0.01	18	0.7	3.5	272	0.01
KL36-06	701.5	704.5	0.131		1310	0.03	2.3	46	160	450	25	1	14	38	3.0	258	0.01
KL36-06	704.5	707.5	0.0215		215	0.01	0.1	22	16	8	45	0.01	6	0.2	0.8	208	0.01
KL36-06	707.5	710.5	0.0237		237	0.03	0.1	20	11	20	35	0.01	10	1.3	2.6	249	0.01
KL36-06	710.5	713.5	0.0203		203	0.02	0.1	21	12	3	32	0.01	7	0.3	1.8	224	0.01
KL36-06	713.5	716.5	0.066		660	0.04	0.1	26	13	2	56	0.01	4	0.4	1.0	260	0.01
KL36-06	716.5	719.5	0.0329		329	0.02	0.1	27	12	13	19	0.01	5	0.5	0.9	291	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL36-06	719.5	721.2	0.06	600	0.03	0.1	16	15	19	30	0.01	6	1.9	1.3	223	0.01
KL36-06	721.2	725.5	0.045	450	0.01	0.1	18	14	3	17	0.01	4	0.4	0.5	200	0.01
KL36-06	725.5	727.9	0.0384	384	0.02	0.1	24	7	17	26	0.01	3	1.2	1.0	206	0.01
KL36-06	727.9	731	0.08	800	0.02	0.1	49	20	19	42	0.01	2	0.9	1.9	172	0.01
KL36-06	731	733.3	0.0109	109	0.01	1	59	27	10	39	3	3	0.7	0.5	187	0.01
KL36-06	733.3	734.6	0.0168	168	0.01	0.1	28	24	5	24	0.01	3	0.4	0.5	166	0.01
KL36-06	734.6	737.5	0.06	600	0.01	0.1	61	27	4	46	0.01	2	0.4	0.6	185	0.01
KL36-06	737.5	740.5	0.0354	354	0.01	0.1	41	18	5	32	0.01	3	0.4	0.8	150	0.01
KL36-06	740.5	743.1	0.047	470	0.01	0.1	27	7	7	54	0.01	4	0.6	1.2	181	0.01
KL36-06	743.1	744.8	0.076	760	0.01	0.1	19	8	18	27	0.01	3	0.5	0.0	196	0.01
KL36-06	744.8	747.5	0.192	1920	0.05	0.1	19	27	12	92	0.01	2	0.4	2.0	25	0.01
KL36-06	747.5	749.5	0.143	1430	0.02	0.1	14	16	9	50	0.01	2	0.6	0.8	39	0.01
KL36-06	749.5	752.5	0.095	950	0.01	0.1	32	17	6	26	0.01	2	0.7	0.8	211	0.01
KL36-06	752.5	755.5	0.088	880	0.03	0.1	21	8	0.01	24	0.01	3	0.2	0.7	178	0.01
KL36-06	755.5	758.5	0.078	780	0.04	0.1	23	9	7	27	0.01	2	0.2	1.0	219	0.01
KL36-06	758.5	761.5	0.144	1440	0.05	0.1	42	11	8	44	0.01	2	0.5	1.4	172	0.01
KL36-06	761.5	764.5	0.0225	225	0.01	0.1	14	12	16	96	0.01	5	0.7	1.5	270	0.01
KL36-06	764.5	767.5	0.0418	418	0.01	0.6	52	50	63	39	0.01	1	1.1	0.9	245	0.01
KL36-06	767.5	770.5	0.065	650	0.03	0.7	119	180	51	57	0.01	1	1.1	1.3	195	0.01
KL36-06	770.5	773.5	0.065	650	0.03	0.1	86	34	5	78	0.01	4	0.4	1.2	65	0.01
KL36-06	773.5	776.5	0.079	790	0.08	0.1	16	6	0.01	57	0.01	14	0.3	3.2	176	0.01
KL36-06	776.5	779.5	0.0294	294	0.01	0.1	16	6	0.01	48	0.01	4	0.01	1.0	191	0.01
KL36-06	779.5	782.5	0.0301	301	0.02	0.1	26	7	1	44	0.01	8	0.01	2.7	126	0.01
KL36-06	782.5	785.5	0.062	620	0.03	0.1	78	38	13	74	0.01	3	0.7	1.3	176	0.01
KL36-06	785.5	788.5	0.112	1120	0.03	0.1	27	9	5	76	0.01	1	0.2	1.3	208	0.01
KL36-06	788.5	791.5	0.096	960	0.04	0.1	165	240	110	54	0.01	3	3.6	3.1	262	0.01
KL36-06	791.5	794.5	0.078	780	0.02	0.1	21	12	2	39	0.01	3	0.2	1.3	189	0.01
KL36-06	794.5	797.5	0.091	910	0.03	0.1	38	14	0.01	56	0.01	1	0.01	1.5	226	0.01
KL36-06	797.5	800.5	0.157	1570	0.04	0.1	25	9	2	58	0.01	1	0.01	1.8	268	0.01
KL36-06	800.5	803.5	0.095	950	0.03	0.1	62	22	0.01	51	0.01	1	0.01	1.5	259	0.01
KL36-06	803.5	806.5	0.07	700	0.02	0.1	27	9	0.01	28	0.01	1	0.01	0.7	175	0.01
KL36-06	806.5	809.5	0.094	940	0.04	0.1	51	14	4	15	0.01	1	0.01	1.7	156	0.01
KL36-06	809.5	812.5	0.086	860	0.01	0.1	47	17	1	13	0.01	3	0.2	1.1	301	0.01
KL36-06	812.5	815.5	0.071	710	0.01	0.1	75	28	13	24	0.01	1	0.6	1.0	165	0.01
KL36-06	815.5	818.5	0.095	950	0.06	1.4	110	85	23	44	3	2	3.2	1.2	150	0.01
KL36-06	818.5	820.5	0.117	1170	0.03	0.1	30	12	2	21	0.01	1	0.01	0.9	132	0.01
KL36-06	820.5	823.5	0.026	260	0.04	0.1	22	17	14	27	0.01	42	1.9	2.0	166	0.01
KL36-06	823.5	826.6	0.044	440	0.02	0.1	25	24	65	33	0.01	2	1.7	1.0	221	0.01
KL36-06	826.6	829.8	0.172	1720	0.03	0.1	26	10	2	18	0.01	1	0.01	2.0	161	0.01
KL36-06	829.8	833	0.061	610	0.01	0.1	19	9	0.01	21	0.01	1	0.01	0.6	165	0.01
KL36-06	833	836.1	0.067	670	0.02	0.1	18	12	0.01	20	0.01	2	0.01	0.6	164	0.01
KL36-06	836.1	839.2	0.068	680	0.03	0.1	14	6	0.01	28	0.01	1	0.01	1.0	174	0.01
KL36-06	839.2	842.2	0.152	1520	0.07	0.1	16	5	0.01	30	0.01	1	0.01	2.2	138	0.01
KL36-06	842.2	845.2	0.106	1060	0.03	0.1	39	9	7	17	0.01	1	0.01	0.5	158	0.01
KL36-06	845.2	848.3	0.094	940	0.01	0.1	25	5	0.01	21	0.01	1	0.01	0.6	186	0.01
KL36-06	848.3	850.9	0.0378	378	0.01	0.1	29	10	9	42	0.01	1	0.3	0.0	174	0.01
KL36-06	850.9	854	0.05	500	0.02	0.1	20	14	48	15	0.01	1	1.3	1.3	180	0.01
KL36-06	854	857.1	0.045	450	0.01	0.1	48	26	18	27	0.01	3	0.7	0.9	151	0.01
KL36-06	857.1	860.3	0.126	1260	0.03	0.1	19	6	1	16	0.01	2	0.01	1.3	220	0.01
KL36-06	860.3	863.3	0.078	780	0.04	0.1	23	11	1	14	0.01	1	0.01	1.5	208	0.01
KL36-06	863.3	866.5	0.09	900	0.04	0.1	149	24	2	21	0.01	1	0.3	1.9	221	0.01
KL36-06	866.5	869.5	0.098	980	0.04	0.1	38	11	0.01	50	0.01	1	0.01	1.1	223	0.01
KL36-06	869.5	872.5	0.131	1310	0.04	0.1	21	7	1	31	0.01	1	0.01	1.7	175	0.01
KL36-06	872.5	874.5	0.121	1210	0.02	0.1	57	19	13	28	0.01	2	1.4	1.4	203	0.01
KL36-06	874.5	876.5	0.096	960	0.01	0.1	82	26	24	45	0.01	4	1.1	1.3	133	0.01
KL36-06	876.5	878.5	0.0383	383	0.02	0.1	59	17	72	25	1	43	3.6	10.6	192	0.01
KL36-06	878.5	881.5	0.0396	396	0.03	0.1	79	24	19	33	1	9	0.7	2.7	198	0.01
KL36-06	881.5	884.5	0.08	800	0.04	0.1	27	5	1	27	0.01	4	0.01	2.4	170	0.01
KL36-06	884.5	886.5	0.079	790	0.02	0.1	46	19	17	38	0.01	6	0.4	2.9	339	0.01
KL36-06	886.5	889.6	0.032	320	0.01	0.1	16	7	5	32	0.01	59	0.3	6.4	190	0.01
KL36-06	889.6	892.5	0.0204	204	0.03	0.1	41	12	15	70	1	17	3.8	3.0	118	0.01
KL36-06	892.5	894.7	0.0268	268	0.02	0.1	54	18	15	32	0.01	38	3	6.9	138	0.01
KL36-06	894.7	897.8	0.0371	371	0.01	0.1	23	8	2	30	0.01	14	0.01	1.9	103	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL36-06	897.8	900.9	0.06	600	0.02	0.1	14	5	0.01	25	0.01	1	0.01	1.2	154	0.01
KL36-06	900.9	904.1	0.054	540	0.01	0.1	15	6	0.01	36	0.01	3	0.01	1.4	268	0.01
KL36-06	904.1	907.2	0.068	680	0.01	0.1	20	7	0.01	26	0.01	1	0.01	1.0	171	0.01
KL36-06	907.2	909.5	0.043	430	0.01	0.1	31	12	0.01	30	0.01	2	0.01	0.8	95	0.01
KL36-06	909.5	911.3	0.058	580	0.01	0.1	40	10	4	39	0.01	4	0.4	0.9	230	0.01
KL36-06	911.3	913.5	0.158	1580	0.03	0.1	15	5	0.01	30	0.01	1	0.01	2.3	188	0.01
KL36-06	913.5	916.5	0.06	600	0.03	0.1	13	7	0.01	15	0.01	1	0.01	0.6	135	0.01
KL36-06	916.5	919.5	0.104	1040	0.02	1.7	30	22	150	19	1	5	26	1.9	286	0.01
KL36-06	919.5	922.5	0.0363	363	0.01	0.1	35	5	2	20	0.01	4	0.2	0.8	259	0.01
KL36-06	922.5	925.5	0.056	560	0.01	0.1	29	6	0.01	28	0.01	3	0.01	1.2	268	0.01
KL36-06	925.5	928.5	0.061	610	0.01	0.1	32	11	0.01	29	0.01	1	0.3	1.2	311	0.01
KL36-06	928.5	931	0.047	470	0.02	0.1	14	5	0.01	33	0.01	2	0.01	0.9	176	0.01
KL36-06	931	934.1	0.051	510	0.02	0.1	13	5	0.01	33	0.01	3	0.5	0.7	156	0.01
KL36-06	934.1	937.2	0.052	520	0.04	0.1	16	6	0.01	17	0.01	1	0.01	0.9	200	0.01
KL36-06	937.2	940.3	0.109	1090	0.05	0.1	11	5	0.01	25	0.01	1	0.01	1.4	189	0.01
KL36-06	940.3	943.5	0.4	4000	0.15	0.1	9	5	2	11	0.01	1	0.01	1.6	191	0.01
KL36-06	943.5	946.5	0.27	2700	0.11	0.1	53	20	0.01	24	0.01	1	0.01	2.1	189	0.01
KL36-06	946.5	949.5	0.082	820	0.03	0.1	15	8	0.01	36	0.01	1	0.01	1.3	150	0.01
KL36-06	949.5	952.5	0.105	1050	0.03	0.1	43	18	0.01	30	0.01	1	0.01	1.4	407	0.01
KL36-06	952.5	955.5	0.105	1050	0.03	0.1	22	5	0.01	54	0.01	1	0.01	1.6	195	0.01
KL36-06	955.5	958.5	0.061	610	0.01	0.1	21	9	0.01	13	0.01	5	0.01	1.1	197	0.01
KL36-06	958.5	961.5	0.078	780	0.01	0.1	37	9	0.01	26	0.01	1	0.2	1.0	143	0.01
KL36-06	961.5	964.5	0.044	440	0.01	0.1	34	20	5	21	0.01	3	0.01	1.5	315	0.01
KL36-06	964.5	967.5	0.06	600	0.01	0.1	88	22	3	27	0.01	1	0.8	0.8	261	0.01
KL36-06	967.5	970.5	0.062	620	0.02	0.1	38	7	0.01	22	0.01	3	0.01	1.2	219	0.01
KL36-06	970.5	973.5	0.06	600	0.01	0.1	18	7	0.01	26	0.01	14	0.01	1.4	163	0.01
KL36-06	973.5	976.3	0.067	670	0.02	0.1	15	6	0.01	37	0.01	7	0.01	1.7	225	0.01
KL36-06	976.3	979.4	0.101	1010	0.06	0.1	11	5	0.01	52	0.01	5	0.01	1.9	137	0.01
KL36-06	979.4	982.5	0.101	1010	0.03	0.1	20	7	0.01	26	0.01	2	0.01	1.5	233	0.01
KL36-06	982.5	985.5	0.07	700	0.04	0.1	13	5	0.01	57	0.01	3	0.01	1.3	175	0.01
KL36-06	985.5	988.5	0.0317	317	0.01	0.1	12	5	0.01	40	0.01	6	0.01	1.9	119	0.01
KL36-06	988.5	991.5	0.08	800	0.01	0.1	55	8	0.01	54	0.01	6	0.01	1.3	206	0.01
KL36-06	991.5	994.5	0.052	520	0.01	0.1	39	8	0.01	36	0.01	2	0.2	0.8	213	0.01
KL36-06	994.5	997.5	0.0297	297	0.01	0.1	28	6	0.01	20	0.01	7	0.01	1.3	144	0.01
KL36-06	997.5	1000.5	0.025	250	0.01	0.1	117	10	8	43	0.01	5	0.8	1.0	218	0.01
KL36-06	1000.5	1003.5	0.051	510	0.01	0.1	23	5	0.01	24	0.01	6	0.01	1.0	202	0.01
KL36-06	1003.5	1006.5	0.048	480	0.01	0.1	24	1	0.01	25	0.01	5	0.01	0.9	129	0.01
KL36-06	1006.5	1009.4	0.035	350	0.01	0.1	40	10	0.01	13	0.01	12	0.01	1.2	175	0.01
KL36-06	1009.4	1012.5	0.048	480	0.02	0.1	62	10	0.01	11	0.01	8	0.01	1.4	136	0.01
KL36-06	1012.5	1015.5	0.0379	379	0.03	0.1	47	9	0.01	13	0.01	10	0.01	0.9	123	0.01
KL36-06	1015.5	1018.5	0.07	700	0.02	0.1	45	6	0.01	26	0.01	6	0.01	0.7	106	0.01
KL36-06	1018.5	1021.5	0.06	600	0.02	0.1	33	6	0.01	13	0.01	16	0.01	2.8	128	0.01
KL36-06	1021.5	1024	0.1	1000	0.02	0.1	18	7	0.01	12	0.01	11	0.01	0.9	69	0.01
KL36-06	1024	1027	0.06	600	0.02	0.1	16	7	0.01	18	0.01	10	0.01	0.9	118	0.01
KL36-06	1027	1030.1	0.085	850	0.02	0.1	69	5	0.01	10	0.01	10	0.01	0.8	72	0.01
KL36-06	1030.1	1033.2	0.12	1200	0.03	0.1	31	6	0.01	12	0.01	6	0.01	0.8	129	0.01
KL36-06	1033.2	1036.3	0.144	1440	0.02	0.1	15	5	0.01	20	0.01	6	0.01	0.8	168	0.01
KL36-06	1036.3	1039.4	0.176	1760	0.12	0.1	54	13	2	16	0.01	15	0.01	2.2	84	0.01
KL36-06	1039.4	1042.5	0.101	1010	0.04	0.1	28	5	0.01	9	0.01	6	0.01	0.5	72	0.01
KL36-06	1042.5	1045.5	0.057	570	0.09	0.1	80	53	38	17	0.01	5	0.4	1.5	76	0.01
KL36-07	0	7.3	0.0013	13	0.02	0.9	570	357	7	2	0.01	1	1.5	2.8	14	0.01
KL36-07	7.3	10.3	0.0019	19	0.01	0.7	214	165	4	2	0.01	1	0.6	2.0	16	0.01
KL36-07	10.3	12.7	0.0026	26	0.03	1.1	860	850	6	7	0.01	1	2.6	2.3	16	0.01
KL36-07	12.7	14.8	0.0021	21	0.04	0.9	530	375	7	2	0.01	1	1.6	2.3	16	0.01
KL36-07	14.8	17.6	0.0015	15	0.02	0.1	107	78	9	3	0.01	1	0.9	1.3	20	0.01
KL36-07	17.6	20.7	0.0017	17	0.02	0.1	93	56	6	1	0.01	1	0.7	0.6	16	0.01
KL36-07	20.7	23	0.0022	22	0.04	1.1	780	550	9	3	0.01	1	1.8	2.8	18	0.01
KL36-07	23	26	0.0009	9	0.05	0.8	670	308	9	1	0.01	1	1	2.0	18	0.01
KL36-07	26	28.5	0.001	10	0.04	0.9	520	530	9	1	0.01	1	1.1	2.6	19	0.01
KL36-07	28.5	32	0.0027	27	0.08	2.4	1270	1170	13	2	0.01	1	3.3	2.8	21	0.01
KL36-07	32	35	0.0126	126	0.09	29	1370	11800	40	2	0.01	1	58	13.5	17	0.1
KL36-07	35	38	0.0046	46	0.03	18	810	6400	17	1	0.01	1	32	5.5	15	0.01
KL36-07	38	41	0.0014	14	0.07	0.8	850	440	8	2	0.01	1	3.4	2.5	15	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL36-07	41	44	0.001		10	0.04	0.9	1100	500	12	1	0.01	1	5.4	2.8	23	0.01
KL36-07	44	47	0.0018		18	0.06	0.8	1150	650	16	3	0.01	1	6.8	2.3	24	0.01
KL36-07	47	51	0.063	630	0.03	0.8	970	580	8	30	0.01	1	5.7	2.0	23	0.01	
KL36-07	51	56	0.002		20	0.06	0.9	940	510	8	4	0.01	1	2.7	2.3	29	0.01
KL36-07	56	59	0.0037		37	0.07	1.1	1290	790	16	3	0.01	1	2.5	2.3	34	0.01
KL36-07	59	65	0.0015		15	0.03	0.6	690	560	4	1	0.01	1	1	1.5	29	0.01
KL36-07	65	68	0.001		10	0.01	0.1	510	490	3	1	0.01	1	1.1	1.5	30	0.01
KL36-07	68	71	0.0008		8	0.01	0.6	540	490	5	1	0.01	1	0.9	1.7	23	0.01
KL36-07	71	74	0.0009		9	0.01	0.6	550	550	3	1	0.01	1	0.8	1.9	23	0.01
KL36-07	74	80	0.001		10	0.06	0.1	530	450	2	1	0.01	1	0.7	1.5	27	0.01
KL36-07	80	83	0.0019		19	0.05	1.2	620	700	5	1	0.01	1	0.01	3.0	34	0.01
KL36-07	83	89	0.0014		14	0.04	0.6	590	560	2	1	0.01	1	2.6	2.0	21	0.01
KL36-07	89	94	0.0016		16	0.01	0.8	800	600	9	1	0.01	1	0.7	2.8	18	0.01
KL36-07	94	98	0.0026		26	0.07	1.2	960	1110	15	2	0.01	1	1.3	6.8	20	0.01
KL36-07	98	107	0.0013		13	0.09	0.7	440	510	12	2	0.01	1	1.5	1.8	22	0.01
KL36-07	107	110	0.0009		9	0.05	0.1	500	398	9	1	0.01	1	1.5	1.5	23	0.01
KL36-07	110	118.8	0.0033		33	0.04	3.9	2880	4750	26	1	0.01	1	6	5.8	21	0.01
KL36-07	118.8	122.7	0.0025		25	0.03	1.4	1100	1010	11	3	0.01	1	4.1	5.3	23	0.01
KL36-07	122.7	128	0.0022		22	0.01	0.8	1050	660	8	1	0.01	1	1.2	3.5	20	0.01
KL36-07	128	131	0.0019		19	0.01	0.1	570	324	12	1	0.01	1	0.7	3.0	24	0.01
KL36-07	131	134.9	0.0018		18	0.01	0.7	1080	430	18	2	0.01	1	2.4	5.5	20	0.01
KL36-07	134.9	137.9	0.002		20	0.01	0.7	1020	580	14	2	0.01	1	1.8	6.2	14	0.01
KL36-07	137.9	140.8	0.0016		16	0.03	0.9	1070	720	10	2	0.01	1	2.1	7.8	19	0.01
KL36-07	140.8	143	0.0012		12	0.01	0.1	420	253	5	1	0.01	1	1.5	2.5	19	0.01
KL36-07	143	146	0.0013		13	0.01	0.5	440	359	7	3	0.01	1	1.3	3.3	20	0.01
KL36-07	146	148.6	0.0016		16	0.01	0.5	690	430	7	1	0.01	1	1.1	4.0	16	0.01
KL36-07	148.6	151.5	0.0013		13	0.01	0.7	740	740	6	1	0.01	1	2.1	3.5	16	0.01
KL36-07	151.5	155	0.0017		17	0.01	0.8	1920	1050	10	1	0.01	1	2	8.3	11	0.01
KL36-07	155	158	0.0027		27	0.01	0.5	790	376	10	9	0.01	1	1.9	4.8	16	0.01
KL36-07	158	161	0.001		10	0.04	0.9	460	240	17	4	0.01	1	0.8	2.8	8	0.01
KL36-07	161	164	0.0027		27	0.02	1	980	790	16	6	0.01	1	1.7	4.3	9	0.01
KL36-07	164	167	0.0019		19	0.01	2.1	2500	1700	25	4	0.01	1	4.8	5.3	11	0.01
KL36-07	167	170	0.0027		27	0.05	4	4890	4720	33	4	5	1	7.3	13.4	15	0.01
KL36-07	170	174	0.0036		36	0.04	6.2	7500	10600	56	4	2	1	13.9	12.5	13	0.1
KL36-07	174	176	0.0028		28	0.01	2.2	3760	2360	21	3	1	1	2.5	6.3	9	0.01
KL36-07	176	179	0.0033		33	0.03	2.3	10100	3000	25	2	0.01	1	3.2	7.5	8	0.18
KL36-07	179	181	0.0018		18	0.03	0.9	1570	920	17	4	0.01	1	1.4	4.8	9	0.01
KL36-07	181	184.6	0.0023		23	0.02	0.1	410	282	11	11	0.01	1	0.7	1.8	10	0.01
KL36-07	184.6	187.7	0.0048		48	0.07	8.3	8000	11200	70	5	3	1	18	20.0	8	0.11
KL36-07	187.7	190.8	0.0016		16	0.15	2.1	2640	1450	31	4	0.01	1	2.7	4.3	9	0.01
KL36-07	190.8	193.9	0.0018		18	0.03	1.8	2360	1190	22	5	0.01	1	2.6	5.3	8	0.01
KL36-07	193.9	196	0.0042		42	0.03	2.2	2140	2390	23	6	0.01	1	2.6	6.0	9	0.01
KL36-07	196	199	0.0031		31	0.09	4.7	3400	2400	56	8	0.01	1	6.2	10.0	8	0.01
KL36-07	199	203	0.0128		128	0.16	38	39600	27500	260	21	3	1	64	30.0	10	0.88
KL36-07	203	206	0.0306		306	0.05	11.9	48900	18700	24	20	1	1	17.5	17.5	15	0.13
KL36-07	206	208.5	0.049		490	0.04	9	47300	12500	31	51	3	1	11.1	17.0	13	0.18
KL36-07	208.5	212	0.001		10	0.01	0.1	139	83	5	10	0.01	1	0.9	1.8	11	0.01
KL36-07	212	215	0.0023		23	0.02	0.6	325	171	6	34	0.01	1	0.6	3.3	11	0.01
KL36-07	215	218	0.001		10	0.02	0.8	346	170	7	44	0.01	1	0.9	4.0	9	0.01
KL36-07	218	220.5	0.0033		33	0.01	0.1	204	154	6	43	0.01	1	0.3	2.3	13	0.01
KL36-07	220.5	222.5	0.0046		46	0.02	1.6	3000	2850	6	34	0.01	1	2.5	4.0	15	0.01
KL36-07	222.5	225.5	0.0272		272	0.03	6.2	10100	10600	35	73	3	1	15.1	14.0	19	0.01
KL36-07	225.5	228.9	0.0045		45	0.01	0.6	84	168	5	20	0.01	1	0.01	1.3	20	0.01
KL36-07	228.9	233	0.0068		68	0.01	1.2	640	1440	6	24	1	3	0.8	2.8	16	0.01
KL36-07	233	236	0.0242		242	0.03	1.1	328	660	7	45	1	2	0.3	3.0	22	0.01
KL36-07	236	239	0.0059		59	0.01	1.2	800	850	9	58	3	1	1	2.6	19	0.01
KL36-07	239	242	0.0071		71	0.03	0.7	219	284	10	42	2	1	0.6	2.3	13	0.01
KL36-07	242	245.8	0.0243		243	0.01	8.2	3710	3170	15	29	19	1	1.4	4.1	13	0.01
KL36-07	245.8	249.1	0.0081		81	0.01	1.7	1310	1250	21	29	2	1	0.7	3.0	16	0.01
KL36-07	249.1	252	0.0106		106	0.02	2.3	1180	1410	15	37	4	1	0.5	4.0	13	0.01
KL36-07	252	254.5	0.0105		105	0.01	2.3	1920	1100	9	51	6	3	0.5	3.0	14	0.01
KL36-07	254.5	256.5	0.0148		148	0.01	4.2	1240	920	13	122	8	1	0.7	3.3	18	0.01
KL36-07	256.5	259.2	0.0206		206	0.01	6.2	8700	1560	11	126	12	1	1.2	7.0	18	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL36-07	259.2	262	0.0362		362	0.01	2.9	4440	354	18	70	15	4	2.1	8.1	21	0.01
KL36-07	262	265	0.17		1700	0.04	22.1	13800	2200	30	130	59	2	12.6	16.5	15	0.01
KL36-07	265	268	0.148		1480	0.06	15	9300	1500	44	67	47	4	3.4	12.8	18	0.01
KL36-07	268	271.2	0.53		5300	0.08	21.6	29800	3300	65	202	55	22	2.7	34.6	33	0.01
KL36-07	271.2	273.8	0.0245		245	0.06	3.3	2400	1230	26	10	8	4	1.9	8.5	15	0.01
KL36-07	273.8	276.8	0.072		720	0.03	4.5	4050	1220	45	10	13	5	2	7.8	20	0.01
KL36-07	276.8	279.8	0.27		2700	0.09	12	30000	16600	62	28	19	9	3.6	21.0	30	0.01
KL36-07	279.8	282	0.67		6700	0.16	10.1	14200	6100	73	68	12	14	2.6	22.0	34	0.01
KL36-07	282	284	0.87		8700	0.15	7.7	9300	5900	85	29	11	9	3.7	21.0	21	0.01
KL36-07	284	287	0.98		9800	0.17	6.6	8700	3400	84	53	8	18	3.5	26.0	36	0.01
KL36-07	287	290	0.449		4490	0.2	2	3370	275	65	60	8	18	1.8	13.0	22	0.01
KL36-07	290	293	0.248		2480	0.17	2.4	4620	1460	110	8	9	12	4.7	19.6	31	0.01
KL36-07	293	296	0.95		9500	0.43	2.2	800	164	43	61	8	41	13.1	11.8	39	0.01
KL36-07	296	299	1.39		13900	0.23	2.1	168	57	33	52	2	30	1.2	11.0	40	0.01
KL36-07	299	302	2.46		24600	0.53	3	161	45	23	40	1	28	0.6	19.0	69	0.01
KL36-07	302	305	0.36		3600	0.11	0.6	89	26	13	29	1	19	0.01	6.3	55	0.01
KL36-07	305	307.8	0.296		2960	0.22	0.9	500	301	35	43	0.01	10	1.1	5.0	63	0.01
KL36-07	307.8	309.2	0.113		1130	0.05	0.1	87	20	5	87	1	11	0.2	4.0	36	0.01
KL36-07	309.2	311.5	0.88		8800	0.43	1.3	351	150	33	21	2	20	2.5	9.5	67	0.01
KL36-07	311.5	314	0.95		9500	0.52	1	1710	80	25	60	1	19	1.2	10.3	99	0.01
KL36-07	314	317	0.87		8700	0.67	1.1	720	275	44	60	2	39	9.8	22.4	133	0.01
KL36-07	317	320	0.484		4840	0.47	1.2	580	270	38	21	1	15	4.2	2.3	90	0.01
KL36-07	320	323	0.48		4800	0.29	2.9	650	760	58	72	3	13	2.5	6.3	108	0.01
KL36-07	323	326	1.12		11200	0.33	10.4	720	740	120	32	38	14	3.1	16.4	122	0.01
KL36-07	326	328.4	0.21		2100	0.2	5.3	351	300	110	96	17	18	3.2	21.5	211	0.01
KL36-07	328.4	332	0.276		2760	0.2	3.3	160	73	88	174	6	44	7.4	40.2	223	0.01
KL36-07	332	334.9	0.57		5700	0.26	3.8	130	64	34	56	6	25	3.7	24.5	180	0.01
KL36-07	334.9	338.5	0.475		4750	0.17	5.1	130	187	32	12	11	8	2	14.7	152	0.01
KL36-07	338.5	341.6	0.443		4430	0.22	6.8	230	121	9	18	6	11	1.8	11.6	109	0.01
KL36-07	341.6	344.8	1.09		10900	0.34	19.4	650	406	100	187	9	29	1.9	31.0	162	0.01
KL36-07	344.8	348.1	1.26		12600	0.38	13.3	311	142	41	233	14	23	1.7	29.0	131	0.01
KL36-07	348.1	350.3	0.61		6100	0.07	2.2	130	121	30	189	3	6	1	10.5	72	0.01
KL36-07	350.3	353.1	0.8		8000	0.04	3	381	219	11	259	2	5	0.6	13.5	82	0.01
KL36-07	353.1	356	2.18		21800	0.62	3.1	279	53	16	62	3	26	1.7	21.0	126	0.01
KL36-07	356	359	2.4		24000	1.28	3.5	1690	760	17	22	5	24	3.2	13.0	65	0.01
KL36-07	359	362	2.34		23400	1.12	3.3	730	580	11	13	7	28	4	33.5	63	0.01
KL36-07	362	365	0.96		9600	1.08	1.7	4200	189	17	33	3	42	1.4	8.3	59	0.01
KL36-07	365	367.9	1.95		19500	2.76	4	30800	140	57	30	11	111	2.5	29.0	72	0.01
KL36-07	367.9	371	0.79		7900	0.72	2.2	940	50	12	31	24	34	0.5	24.6	79	0.01
KL36-07	371	373.6	2.45		24500	2.03	3.5	780	34	3	17	2	28	0.2	27.0	40	0.01
KL36-07	373.6	376.6	3.32		33200	2.51	5.1	1080	80	1	13	2	23	0.2	20.0	32	0.01
KL36-07	376.6	379.7	0.83		8300	0.67	2.1	540	68	4	3	5	21	0.4	14.8	36	0.01
KL36-07	379.7	382.8	2.03		20300	2.28	2.6	930	22	2	2	2	25	0.01	14.0	38	0.01
KL36-07	382.8	385.9	2.04		20400	1.56	2.9	680	26	2	5	2	23	0.01	19.0	35	0.01
KL36-07	385.9	389	1.61		16100	1.64	2.4	490	67	1	2	3	23	0.01	14.0	30	0.01
KL36-07	389	392	2.07		20700	2.54	3.2	351	22	0.01	2	2	17	0.01	21.0	36	0.01
KL36-07	392	395	3.7		37000	4.86	6.8	750	34	2	28	2	26	0.01	26.0	43	0.01
KL36-07	395	398.3	1.9		19000	2.08	9.3	1290	197	5	31	4	32	0.4	18.0	97	0.01
KL36-07	398.3	400.5	0.68		6800	0.34	6.1	7200	39	11	27	4	68	0.6	59.8	83	0.01
KL36-07	400.5	404.2	0.72		7200	0.4	8.1	135	21	6	7	2	12	0.6	12.3	42	0.01
KL36-07	404.2	407.2	0.66		6600	0.36	6.4	81	28	5	5	4	7	0.3	10.8	70	0.01
KL36-07	407.2	411	1.63		16300	1.18	7.8	160	27	8	9	8	7	0.5	19.0	50	0.01
KL36-07	411	413.2	4.06		40600	1.4	9	106	14	4	11	2	11	0.2	29.0	150	0.01
KL36-07	413.2	415.2	2.97		29700	0.46	5.9	45	13	4	50	1	12	1.1	33.0	56	0.01
KL36-07	415.2	418.7	2.32		23200	0.34	3	37	18	6	67	0.01	11	1.2	22.0	80	0.01
KL36-07	418.7	421.6	1.18		11800	0.18	1.7	25	9	3	383	1	7	0.3	14.5	87	0.01
KL36-07	421.6	424.2	0.98		9800	0.06	0.1	16	5	0.01	185	0.01	5	0.01	9.3	110	0.01
KL36-07	424.2	427.3	0.71		7100	0.05	0.1	26	17	1	161	0.01	5	0.01	8.3	90	0.01
KL36-07	427.3	431.2	0.529		5290	0.09	0.9	38	26	3	398	1	10	0.4	11.3	128	0.01
KL36-07	431.2	434.3	0.64		6400	0.17	1.1	43	16	2	156	0.01	6	0.01	7.3	43	0.01
KL36-07	434.3	437.6	0.521		5210	0.16	1.3	130	30	23	122	2	10	0.6	12.0	45	0.01
KL36-07	437.6	440.2	0.365		3650	0.13	1.5	157	34	57	50	1	7	2.8	11.3	65	0.01
KL36-07	440.2	442.4	0.526		5260	0.14	1.5	278	64	45	39	2	4	5.2	7.7	57	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL36-07	442.4	445.9	0.302	3020	0.09	0.8	1180	55	62	96	1	6	13.4	7.5	69	0.01
KL36-07	445.9	448.5	0.351	3510	0.12	0.9	134	25	52	610	3	5	5.8	8.0	103	0.01
KL36-07	448.5	451.7	0.047	470	0.09	0.1	405	28	25	275	1	10	2.8	9.8	104	0.01
KL36-07	451.7	455	0.025	250	0.09	0.1	450	357	6	220	1	18	1.3	10.2	116	0.01
KL36-07	455	458	0.31	3100	0.11	1.1	139	34	280	199	1	4	5.2	8.8	110	0.01
KL36-07	458	460.9	0.0304	304	0.08	0.1	490	440	7	284	1	6	0.5	7.3	143	0.01
KL36-07	460.9	464	0.0399	399	0.1	0.1	250	30	8	260	2	26	1.2	8.0	118	0.01
KL36-07	464	467.1	0.019	190	0.05	0.1	53	6	6	240	1	9	0.5	5.9	145	0.01
KL36-07	467.1	470.5	0.0116	116	0.03	0.1	25	7	7	135	0.01	4	0.3	1.8	124	0.01
KL36-07	470.5	474.6	0.0103	103	0.02	0.1	12	6	3	89	0.01	2	0.01	1.2	182	0.01
KL36-08	0	2.6	0.0059	59	0.05	1.4	470	287	11	13	3	1	1.3	1.9	15	0.01
KL36-08	2.6	4.6	0.0031	31	0.04	0.5	440	122	3	6	0.01	1	1.1	2.1	16	0.01
KL36-08	4.6	7.4	0.0016	16	0.03	0.7	580	231	4	2	0.01	1	1.5	2.7	16	0.01
KL36-08	7.4	9.7	0.0017	17	0.02	0.9	590	277	3	1	0.01	1	1.6	1.9	17	0.01
KL36-08	9.7	12.4	0.0018	18	0.03	1.1	550	271	4	8	2	1	1.4	1.7	15	0.01
KL36-08	12.4	15.1	0.0012	12	0.11	1.2	980	358	17	4	0.01	1	2.5	3.2	20	0.01
KL36-08	15.1	18	0.0056	56	0.03	0.1	290	98	7	5	0.01	1	0.9	1.7	15	0.01
KL36-08	18	20.6	0.0051	51	0.03	0.1	143	59	7	3	0.01	1	1.7	1.6	17	0.01
KL36-08	20.6	23.6	0.001	10	0.02	0.1	276	102	12	3	0.01	1	0.6	2.4	15	0.01
KL36-08	23.6	26.6	0.0133	133	0.04	0.7	440	175	11	5	0.01	1	1.1	1.9	23	0.01
KL36-08	26.6	29.7	0.0028	28	0.1	1	630	249	13	2	0.01	1	2.1	1.9	68	0.1
KL36-08	29.7	32.6	0.0042	42	0.11	1.4	1690	580	19	24	0.01	1	7.1	2.3	20	0.1
KL36-08	32.6	35.6	0.0045	45	0.01	0.9	244	150	6	6	0.01	1	1.7	1.2	19	0.01
KL36-08	35.6	38.6	0.0031	31	0.01	1.2	409	340	14	3	0.01	1	3.1	1.3	29	0.01
KL36-08	38.6	41.6	0.018	180	0.09	7.4	4900	4300	77	3	0.01	1	25	1.8	36	0.1
KL36-08	41.6	44.6	0.0072	72	0.21	7.3	3000	2400	51	4	1	1	9.2	3.2	24	0.11
KL36-08	44.6	47.6	0.048	480	0.13	1.2	580	329	9	7	0.01	2	3.4	2.9	49	0.01
KL36-08	47.6	50.6	0.0071	71	0.03	1.4	750	334	7	2	1	1	1.2	1.7	25	0.01
KL36-08	50.6	53.6	0.0135	135	0.08	1.3	450	234	10	9	0.01	1	1.7	2.4	30	0.01
KL36-08	53.6	56.6	0.0044	44	0.01	1.4	142	122	8	3	5	1	0.8	2.1	22	0.01
KL36-08	56.6	59.6	0.0012	12	0.01	0.6	107	53	9	3	0.01	1	0.6	1.7	29	0.01
KL36-08	59.6	62.6	0.0072	72	0.01	0.7	120	70	14	5	0.01	2	0.6	1.5	23	0.01
KL36-08	62.6	65.6	0.0026	26	0.04	2.9	181	407	12	7	7	1	1	2.6	19	0.01
KL36-08	65.6	66.8	0.0047	47	0.23	0.8	490	207	14	3	0.01	1	2	3.0	18	0.01
KL36-08	66.8	69.8	0.058	580	0.05	1.5	470	221	20	17	3	2	7.8	3.5	41	0.01
KL36-08	69.8	71.6	0.0296	296	0.03	0.9	440	173	14	9	13	2	1.9	3.2	31	0.01
KL36-08	71.6	74.6	0.0202	202	0.05	2.5	710	1200	25	6	0.01	2	4.2	4.8	25	0.01
KL36-08	74.6	77.1	0.0034	34	0.03	3.1	1680	3300	20	3	0.01	1	7.1	6.0	25	0.19
KL36-08	77.1	79	0.0023	23	0.01	1.7	1390	1450	42	3	0.01	1	3.5	8.3	30	0.01
KL36-08	79	80.6	0.0025	25	0.01	1	228	700	26	5	1	1	1.3	7.3	28	0.01
KL36-08	80.6	83.6	0.003	30	0.01	0.5	105	251	17	4	0.01	2	1.1	1.7	22	0.01
KL36-08	83.6	86.6	0.0024	24	0.01	0.5	122	381	18	2	0.01	2	1.3	2.2	26	0.01
KL36-08	86.6	89.6	0.0189	189	0.08	1.9	570	201	60	4	1	2	9.8	4.2	30	0.12
KL36-08	89.6	91.9	0.0051	51	0.04	0.1	172	120	17	4	2	1	2.3	4.4	21	0.01
KL36-08	91.9	95	0.0233	233	0.04	0.5	152	92	17	8	1	2	1	4.5	20	0.01
KL36-08	95	98	0.0023	23	0.03	0.1	92	84	18	3	0.01	1	0.8	1.2	27	0.01
KL36-08	98	101.1	0.0012	12	0.02	0.1	99	192	20	1	0.01	2	0.8	1.5	33	0.01
KL36-08	101.1	104.1	0.0105	105	0.01	0.1	89	88	9	2	0.01	1	0.6	1.8	20	0.01
KL36-08	104.1	107.2	0.0015	15	0.03	0.1	222	156	4	2	1	1	0.6	2.0	16	0.01
KL36-08	107.2	110.3	0.0022	22	0.01	0.5	221	163	5	9	3	1	0.9	2.6	19	0.01
KL36-08	110.3	112.9	0.0034	34	0.01	1.1	420	177	10	71	8	1	1.5	2.5	22	0.01
KL36-08	112.9	115.7	0.0037	37	0.02	1.3	298	275	26	126	49	2	2	3.4	38	0.01
KL36-08	115.7	117.9	0.0073	73	0.6	2.9	18200	1870	250	23	6	1	26	12.2	29	0.78
KL36-08	117.9	119.6	0.0345	345	0.05	5.6	1270	850	67	44	17	1	15.7	5.7	30	0.11
KL36-08	119.6	122.6	0.0109	109	0.16	2.7	6600	1400	57	4	5	1	16.5	12.8	33	0.54
KL36-08	122.6	125.1	0.0116	116	0.09	2	5300	1900	56	3	6	1	9.5	13.6	40	0.11
KL36-08	125.1	127.1	0.0191	191	0.13	1.4	670	239	35	5	4	4	4.5	2.2	34	0.01
KL36-08	127.1	128.6	0.078	780	0.34	2.2	157	132	33	126	36	7	7.8	12.5	64	0.01
KL36-08	128.6	131.6	0.028	280	0.06	0.9	219	150	28	34	7	1	6.9	4.2	112	0.01
KL36-08	131.6	134.6	0.06	600	0.1	1.3	237	205	21	33	6	4	4.8	0.7	75	0.01
KL36-08	134.6	137.1	0.096	960	0.05	1.9	520	278	25	27	2	2	14.9	4.1	64	0.01
KL36-08	137.1	139.7	4.85	48500	1.08	170	19900	8500	7500	4	14	12	1730	45.0	167	4.45
KL36-08	139.7	141.5	1.92	19200	0.34	25.8	750	229	3300	73	6	3	700	14.0	206	0.87

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL36-08	141.5	143.6	0.69	6900	0.28	24.7	1380	530	420	64	6	7	62	8.0	340	0.2
KL36-08	143.6	145.9	0.32	3200	2.06	51	8600	14500	630	219	6	7	50	22.9	380	0.62
KL36-08	145.9	147.6	0.19	1900	0.51	21.4	5200	3900	150	72	16	8	11.8	10.5	266	0.32
KL36-08	147.6	149.6	0.168	1680	0.22	8.6	2700	1400	50	79	5	14	5.3	9.4	178	0.14
KL36-08	149.6	151.8	0.58	5800	0.34	22	2200	2100	120	34	8	10	3.2	10.5	48	0.19
KL36-08	151.8	153.7	0.37	3700	0.28	11.3	1630	2100	83	33	4	5	4.3	6.8	44	0.16
KL36-08	153.7	155.6	0.145	1450	0.22	5.8	1050	1630	30	29	4	1	3.4	4.5	42	0.1
KL36-08	155.6	159.4	0.101	1010	0.34	7.2	3500	1430	47	96	4	2	4.1	5.5	375	0.18
KL36-08	159.4	161.2	0.24	2400	2.12	56	17100	23600	510	343	16	2	50	13.0	64	1.24
KL36-08	161.2	164.3	0.189	1890	2.88	62	28900	16200	410	2040	46	4	50	14.7	57	1.75
KL36-08	164.3	166.7	0.0261	261	0.45	8.1	6400	6200	120	480	4	4	13.5	10.0	103	0.34
KL36-08	166.7	169.9	0.14	1400	0.12	3.4	450	820	100	190	1	3	8.8	3.8	104	0.01
KL36-08	169.9	171.8	0.52	5200	0.28	7.6	1450	1400	110	55	10	12	7.4	7.3	30	0.11
KL36-08	171.8	173.6	2.92	29200	2.42	29.8	19200	4300	460	570	710	78	60	55.0	141	0.54
KL36-08	173.6	176.6	0.102	1020	0.18	10.9	10500	7300	100	109	19	3	32	18.1	26	0.88
KL36-08	176.6	179.6	0.056	560	0.5	11.8	4200	3800	79	215	44	4	6.5	14.8	24	0.24
KL36-08	179.6	182.4	0.0318	318	0.2	9.7	2100	1130	40	270	72	1	2.5	12.7	25	0.11
KL36-08	182.4	185	0.0139	139	0.04	6.5	1470	630	14	128	34	1	1.5	4.3	16	0.1
KL36-08	185	187	0.0279	279	0.15	13.8	930	1480	20	151	52	1	2.6	7.8	26	0.01
KL36-08	187	188.6	0.0369	369	0.03	13.5	1920	2130	23	25	41	1	4	13.8	21	0.01
KL36-08	188.6	191.6	0.0332	332	0.04	9.7	3400	4000	20	40	22	1	2	6.4	26	0.01
KL36-08	191.6	194.6	0.0203	203	0.07	21.8	4200	9000	29	78	42	2	5.6	11.3	25	0.12
KL36-08	194.6	197.6	0.0233	233	0.12	54	383	7900	53	104	102	3	5.2	16.4	37	0.01
KL36-08	197.6	200.5	0.0252	252	0.09	21	498	2940	37	64	45	1	3.8	9.2	33	0.01
KL36-08	200.5	203.1	0.0082	82	0.04	5.7	312	1410	11	14	10	1	2.2	4.3	23	0.01
KL36-08	203.1	204.9	0.0058	58	0.03	3.8	216	750	4	25	8	1	1.1	3.0	24	0.01
KL36-08	204.9	207	0.0112	112	0.04	3	420	580	13	68	10	1	0.7	3.7	20	0.01
KL36-08	207	212.2	0.045	450	0.09	9.8	3830	1200	44	21	39	4	3.6	12.2	21	0.01
KL36-08	212.2	215.3	0.0169	169	0.04	1.9	750	600	12	10	5	1	1.4	4.9	24	0.01
KL36-08	215.3	218.4	0.0183	183	0.03	5.1	800	810	10	29	19	1	1.1	4.8	21	0.01
KL36-08	218.4	221	0.0127	127	0.04	2.6	1150	520	10	12	9	1	1.2	7.1	18	0.01
KL36-08	221	223.8	0.006	60	0.01	1.4	1320	600	4	10	6	1	2.2	3.6	8	0.01
KL36-08	223.8	225	0.0096	96	0.03	0.7	470	520	4	17	4	1	1.3	2.4	9	0.01
KL36-08	225	227.3	0.0052	52	0.02	0.7	460	670	9	30	3	1	2.6	3.1	11	0.01
KL36-08	227.3	229.1	0.0032	32	0.01	1.7	460	440	13	17	15	1	3.9	6.2	6	0.01
KL36-08	229.1	230.6	0.0144	144	0.01	24	1020	2230	42	46	130	2	7.2	16.8	11	0.01
KL36-08	230.6	233.6	0.0312	312	0.05	0.6	173	94	18	11	6	5	1.7	4.5	11	0.01
KL36-08	233.6	235.8	0.009	90	0.06	0.1	86	113	4	7	2	1	0.4	2.4	12	0.01
KL36-08	235.8	237	0.07	700	0.05	0.7	227	108	31	5	3	2	5.8	3.8	14	0.01
KL36-08	237	239.6	0.0224	224	0.02	1	590	1070	20	3	3	1	3.4	2.3	8	0.01
KL36-08	239.6	242.2	0.0144	144	0.01	2.1	1000	2060	13	7	3	1	5.8	4.4	11	0.01
KL36-08	242.2	244.8	0.0294	294	0.02	1	264	234	9	8	3	1	3.1	3.6	8	0.01
KL36-08	244.8	247.4	0.109	1090	0.09	1.3	530	22	18	3	5	7	5	1.7	13	0.01
KL36-08	247.4	248.6	0.0083	83	0.01	0.6	211	139	5	15	3	1	0.8	2.9	10	0.01
KL36-08	248.6	251	0.0295	295	0.02	1.6	3390	900	11	16	5	1	2.3	1.6	13	0.01
KL36-08	251	254	0.0257	257	0.03	0.7	680	430	20	9	2	1	3.1	4.8	12	0.01
KL36-08	254	257	0.0108	108	0.03	0.8	950	274	40	4	4	1	4	3.7	7	0.01
KL36-08	257	258.8	0.0263	263	0.24	6.5	5340	2950	50	15	16	2	9.2	11.6	20	0.13
KL36-08	258.8	260.6	0.27	2700	0.13	5.4	1000	430	200	13	7	6	26	4.4	19	0.01
KL36-08	260.6	263.6	0.0081	81	0.01	1	500	297	11	6	5	1	5.1	3.6	14	0.01
KL36-08	263.6	266.6	0.0189	189	0.02	2.4	6160	1460	120	6	2	1	12.9	10.7	15	0.01
KL36-08	266.6	269.6	0.0101	101	0.01	0.1	175	140	21	4	2	1	4.9	2.5	10	0.01
KL36-08	269.6	272.6	0.0089	89	0.01	0.1	480	247	16	9	1	2	4.8	3.7	15	0.01
KL36-08	272.6	275.6	0.049	490	0.05	0.5	810	100	21	6	2	4	5.6	3.2	18	0.01
KL36-08	275.6	278.6	0.0226	226	0.03	0.8	700	308	9	5	1	1	1.8	4.2	8	0.01
KL36-08	278.6	281.6	0.0334	334	0.06	0.8	436	101	60	3	1	2	10.6	2.9	15	0.01
KL36-08	281.6	284.4	0.079	790	0.1	0.7	790	71	52	7	3	7	11.8	5.3	19	0.01
KL36-08	284.4	287.5	0.139	1390	0.04	0.9	610	129	63	14	5	5	17.6	7.4	18	0.01
KL36-08	287.5	290.6	0.098	980	0.03	0.6	450	58	62	10	4	5	6	6.2	16	0.01
KL36-08	290.6	292.3	0.188	1880	0.05	1.2	257	24	22	4	5	18	3.2	1.8	18	0.01
KL36-08	292.3	293.6	0.78	7800	0.5	2.4	235	52	58	33	14	25	10.2	3.7	21	0.01
KL36-08	293.6	295.1	1.1	11000	0.62	2.3	205	74	7	16	10	19	5.3	9.0	34	0.01
KL36-08	295.1	297.2	3.35	33500	1.92	8.8	255	41	10	133	7	28	2.7	9.5	17	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL36-08	297.2	299.6	0.94	9400	0.67	7.7	1850	118	37	130	4	13	1.6	10.2	30	0.01
KL36-08	299.6	302.6	1.58	15800	2.04	13.2	830	132	24	180	22	23	2.3	18.8	70	0.01
KL36-08	302.6	305.6	0.25	2500	0.53	2.7	97	31	21	391	8	8	4.5	4.5	114	0.01
KL36-08	305.6	308.6	0.167	1670	0.06	0.1	83	18	7	262	1	9	1.6	2.0	33	0.01
KL36-08	308.6	310.5	0.29	2900	0.12	1.1	373	36	12	230	2	16	2.3	5.0	21	0.01
KL36-08	310.5	311.6	0.52	5200	0.34	1.2	13100	28	10	46	2	41	2.3	5.7	20	0.01
KL36-08	311.6	314.6	0.162	1620	0.11	7.2	1590	590	240	4	14	2	3.2	1.5	17	0.16
KL36-08	314.6	317.6	0.308	3080	0.17	0.9	227	61	12	192	1	10	6.4	4.5	15	0.01
KL36-08	317.6	320.6	0.206	2060	0.2	0.5	183	39	17	201	1	11	2.2	4.0	17	0.01
KL36-08	320.6	323.6	0.146	1460	0.12	0.1	220	25	13	84	0.01	10	1.3	2.0	27	0.01
KL36-08	323.6	326.6	0.469	4690	0.79	18.4	4960	3000	320	11	34	8	10	1.8	21	0.18
KL36-08	326.6	329.6	0.67	6700	0.52	1.5	285	42	38	12	3	15	3	7.8	25	0.01
KL36-08	329.6	332.6	0.352	3520	0.25	0.7	173	31	12	65	2	10	2.5	4.5	19	0.01
KL36-08	332.6	335.6	0.21	2100	0.12	0.6	90	33	7	77	0.01	4	1.5	3.5	12	0.01
KL36-08	335.6	338.6	0.84	8400	0.38	1.3	223	32	16	106	0.01	18	4.6	7.0	20	0.01
KL36-08	338.6	341.6	2.68	26800	1.01	3.4	363	17	18	70	1	33	2.8	10.0	24	0.01
KL36-08	341.6	344.6	0.0117	117	0.01	0.1	70	56	12	3	0.01	8	0.2	0.0	51	0.01
KL36-08	344.6	347.4	0.109	1090	0.07	0.8	244	43	47	6	6	6	1.2	1.3	20	0.01
KL36-08	347.4	350.5	0.21	2100	0.14	0.9	810	30	25	5	6	6	1.4	4.0	23	0.01
KL36-08	350.5	353.6	0.512	5120	0.38	2.5	610	18	63	4	4	21	1.7	8.3	21	0.01
KL36-08	353.6	356.6	0.151	1510	0.11	0.7	990	14	23	20	6	6	2.2	4.3	30	0.01
KL36-08	356.6	359.6	0.08	800	0.03	0.1	1290	12	17	4	5	3	1.2	1.3	16	0.01
KL36-08	359.6	362.6	0.055	550	0.04	0.1	700	12	16	3	6	3	0.9	0.6	14	0.01
KL36-08	362.6	364.3	0.22	2200	0.07	2.1	396	15	23	7	10	26	1.9	1.5	21	0.01
KL36-08	364.3	367.3	1.04	10400	0.16	5.7	1590	15	32	6	9	63	4.8	3.8	23	0.01
KL36-08	367.3	369.7	1.02	10200	0.39	3.7	409	178	28	2	7	34	8.5	4.5	37	0.01
KL36-08	369.7	371.6	2.08	20800	0.77	2.2	283	16	10	4	2	37	6.8	7.3	50	0.01
KL36-08	371.6	374.6	0.073	730	0.84	37	4970	3190	870	3	140	6	21.5	3.8	60	0.2
KL36-08	374.6	377.6	1.76	17600	1.45	4.4	281	41	8	25	7	40	1.4	14.8	43	0.01
KL36-08	377.6	380.1	1.64	16400	1.32	3.6	500	104	12	17	5	41	1.4	11.0	53	0.01
KL36-08	380.1	382.1	1.14	11400	0.79	4	630	145	11	53	2	13	0.8	6.5	107	0.01
KL36-08	382.1	383.6	0.9	9000	0.39	40	470	3000	36	6	55	7	4.1	5.5	72	0.01
KL36-08	383.6	386.6	0.83	8300	0.74	1.8	179	17	4	10	1	12	0.6	8.8	86	0.01
KL36-08	386.6	389.6	0.56	5600	0.4	1.9	160	31	4	19	1	11	0.5	6.0	123	0.01
KL36-08	389.6	392.6	0.68	6800	0.34	1.7	142	18	2	42	1	8	0.4	6.5	95	0.01
KL36-08	392.6	394.8	0.74	7400	0.37	2	112	13	2	35	1	10	0.3	5.9	120	0.01
KL36-08	394.8	400	0.23	2300	0.18	0.6	65	9	2	13	0.01	6	0.4	3.3	74	0.01
KL38-02	0	5	0.0035	35	0.2	0.1	211	66	25	4	0.01	1	1	1.2	19	0.01
KL38-02	5	8.7	0.0052	52	0.06	0.1	237	46	11	7	0.01	1	0.6	1.2	16	0.01
KL38-02	8.7	11.7	0.0036	36	0.02	0.8	93	31	8	4	0.01	1	0.6	2.8	19	0.01
KL38-02	11.7	14.7	0.009	90	0.05	0.7	99	28	8	3	0.01	1	1.4	2.2	18	0.01
KL38-02	14.7	18.4	0.0019	19	0.03	0.1	113	30	7	1	0.01	1	0.6	2.0	18	0.01
KL38-02	18.4	21.3	0.0061	61	0.14	1.2	560	234	8	10	0.01	1	1.7	4.5	21	0.01
KL38-02	21.3	25	0.0022	22	0.15	0.6	84	36	7	3	0.01	1	0.4	1.8	51	0.01
KL38-02	25	27.3	0.0034	34	0.36	0.9	322	78	9	1	0.01	1	0.9	1.8	25	0.01
KL38-02	27.3	29.4	0.0031	31	0.26	0.7	124	31	12	3	0.01	1	0.8	3.5	30	0.01
KL38-02	29.4	32.3	0.0141	141	0.26	3.1	2140	1130	40	10	3	1	9.9	14.7	41	0.21
KL38-02	32.3	34.7	0.0027	27	0.14	0.1	73	31	7	3	0.01	1	0.9	2.0	36	0.01
KL38-02	34.7	37.8	0.0018	18	0.12	0.1	101	56	13	6	0.01	1	0.9	2.5	37	0.01
KL38-02	37.8	41.7	0.002	20	0.02	0.1	57	30	5	1	0.01	1	0.4	0.0	44	0.01
KL38-02	41.7	45.8	0.0015	15	0.05	0.1	148	60	5	4	0.01	1	0.6	0.8	40	0.01
KL38-02	45.8	48.8	0.0027	27	0.04	0.1	139	46	10	5	0.01	1	1.2	0.9	24	0.01
KL38-02	48.8	50.6	0.0016	16	0.07	0.7	276	118	15	4	0.01	1	1.8	2.2	40	0.01
KL38-02	50.6	53.7	0.0033	33	0.03	1	246	334	37	5	0.01	1	4	1.3	25	0.01
KL38-02	53.7	55.9	0.0094	94	0.11	9.6	1260	1200	67	6	1	2	7.2	9.3	46	0.16
KL38-02	55.9	59	0.0101	101	0.08	1	91	171	48	2	0.01	1	3.5	1.0	38	0.01
KL38-02	59	62.8	0.0057	57	0.03	0.8	169	184	18	3	0.01	1	2.4	1.5	23	0.01
KL38-02	62.8	65.7	0.0036	36	0.05	1.6	660	320	7	1	0.01	1	2.7	2.8	17	0.01
KL38-02	65.7	68.7	0.0013	13	0.08	1.1	408	132	15	1	0.01	1	3.7	3.8	17	0.01
KL38-02	68.7	71.5	0.0129	129	0.08	1	173	100	9	5	0.01	1	2.1	2.2	16	0.01
KL38-02	71.5	74.6	0.0063	63	0.19	1.5	261	341	43	1	0.01	2	5.4	1.5	46	0.12
KL38-02	74.6	77.7	0.0058	58	0.15	1.7	347	310	41	6	1	1	6	3.0	32	0.1
KL38-02	77.7	80.7	0.0075	75	0.13	2.4	1430	800	40	7	1	1	5.5	6.0	40	0.14

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL38-02	80.7	83.7	0.0113	113	0.2	4.6	920	1280	67	9	7	3	16.7	10.5	54	0.25
KL38-02	83.7	86.7	0.0042	42	0.03	1.2	253	570	19	7	2	1	2.3	1.8	39	0.01
KL38-02	86.7	89.7	0.0099	99	0.32	3	1160	1030	53	5	3	1	14.4	9.8	50	0.28
KL38-02	89.7	92.7	0.0048	48	0.15	2.6	790	1090	31	5	3	1	5.3	5.1	28	0.01
KL38-02	92.7	95.7	0.0059	59	0.68	2.2	990	378	210	7	1	1	12	7.0	59	0.37
KL38-02	95.7	98.7	0.0029	29	0.38	2.1	780	381	70	11	1	1	9.7	6.0	72	0.23
KL38-02	98.7	101.7	0.0039	39	0.33	2.8	1130	580	85	7	3	4	5.4	4.8	70	0.16
KL38-02	101.7	104.9	0.0028	28	0.16	2	1430	680	45	6	2	2	2.5	2.9	141	0.01
KL38-02	104.9	107	0.0132	132	0.56	17.7	8500	7300	47	18	6	7	18.6	11.3	70	0.37
KL38-02	107	109.5	0.115	1150	2	127	56800	59500	160	25	42	2	100	60.5	51	4.15
KL38-02	109.5	113.5	0.332	3320	0.72	19.5	2300	1190	120	26	52	3	19	13.0	207	0.32
KL38-02	113.5	116.7	0.25	2500	1.2	101	11300	7000	330	209	550	3	40	27.0	178	1.5
KL38-02	116.7	119.7	0.076	760	1.2	62	11800	12800	240	145	160	3	9.6	43.0	257	2.12
KL38-02	119.7	122.7	0.055	550	0.27	7.6	1800	2100	100	45	203	3	7.5	8.0	214	0.34
KL38-02	122.7	124.6	0.191	1910	0.59	53	2900	3290	390	14	176	3	9.6	39.5	273	1.06
KL38-02	124.6	127.9	0.0099	99	0.76	11.3	13700	6400	44	16	2	3	2.8	15.0	187	0.51
KL38-02	127.9	130.4	0.0057	57	0.1	2	810	354	22	40	1	1	1.2	4.6	217	0.01
KL38-02	130.4	133.5	0.0029	29	0.44	6.1	3600	1210	32	33	0.01	4	2.4	4.4	184	0.52
KL38-02	133.5	135.7	0.008	80	0.75	5.9	1120	430	210	540	3	3	5.4	1.5	149	0.13
KL38-02	135.7	137.7	0.0033	33	0.48	2.7	1350	530	66	530	1	2	3.9	6.1	208	0.11
KL38-02	137.7	142.2	0.0236	236	0.96	4.5	4700	1880	200	2000	3	2	23	11.5	145	0.56
KL38-02	142.2	146.2	0.0108	108	0.61	1.8	1030	530	33	1125	1	1	4.2	4.0	57	0.13
KL38-02	146.2	149.7	0.083	830	1.59	8.5	17600	10800	540	1075	2	2	34	11.0	80	1.55
KL38-02	149.7	155.7	0.196	1960	2.19	21.4	34900	12800	990	590	22	3	119	21.0	66	3.64
KL38-02	155.7	159.9	0.097	970	1.44	11.4	22900	2100	370	564	17	6	137	25.0	38	1.52
KL38-02	159.9	162.9	0.0092	92	0.27	3.5	2360	530	27	82	2	1	11	6.5	24	0.28
KL38-02	162.9	164.7	0.0192	192	1.43	16	6400	3030	88	28	8	4	22	15.5	27	0.8
KL38-02	164.7	168.4	0.0146	146	0.65	10.3	4700	2470	68	25	5	3	45	11.8	26	0.72
KL38-02	168.4	172	0.008	80	0.96	6.4	3500	2190	85	14	4	3	25	11.5	24	0.63
KL38-02	172	173.7	0.0159	159	1.24	1.4	2480	120	320	550	22	1	14.2	7.0	24	0.39
KL38-02	173.7	176.7	0.168	1680	2.12	13.1	8700	1060	470	359	34	7	37	23.8	21	0.31
KL38-02	176.7	179.7	0.0229	229	0.92	4.4	8700	1020	160	49	6	7	10.7	12.0	32	0.48
KL38-02	179.7	182.7	0.081	810	4.5	44	29800	24200	1180	150	112	4	85	180.0	25	0.13
KL38-02	182.7	185.7	0.39	3900	4.31	200	106000	61500	1160	175	98	3	323	260.0	55	0.6
KL38-02	185.7	190.7	0.25	2500	3.19	118	49300	43100	1190	278	63	6	293	150.0	70	0.83
KL38-02	190.7	194.4	0.31	3100	3.94	123	65800	48300	1270	300	82	6	248	238.0	85	2.14
KL38-02	194.4	197.5	0.112	1120	1.2	45	27600	19100	300	260	27	3	55	81.0	47	0.72
KL38-02	197.5	200	0.26	2600	2.4	69	12800	6500	640	2120	143	15	73	95.0	73	0.36
KL38-02	200	203.2	0.0201	201	0.46	10.8	3500	2150	120	154	20	2	13	27.5	28	0.16
KL38-02	203.2	206.8	0.112	1120	1.55	49	12000	6800	310	229	30	7	43	74.0	47	0.39
KL38-02	206.8	212.8	0.025	250	0.63	18.1	7100	5300	130	59	15	3	26	33.5	26	0.16
KL38-02	212.8	216	0.0047	47	0.22	3.5	510	283	39	20	1	1	6.1	6.0	22	0.01
KL38-02	216	218.8	0.0082	82	0.24	2.3	1600	620	34	14	3	1	9.9	6.8	15	0.1
KL38-02	218.8	221.8	0.0038	38	0.51	1.1	176	43	180	6	0.01	1	3.2	9.0	13	0.12
KL38-02	221.8	224.3	0.0032	32	0.09	0.6	69	35	15	4	1	1	0.8	2.4	11	0.01
KL38-02	224.3	228	0.0046	46	0.11	0.9	298	284	17	2	0.01	1	1.4	9.8	7	0.1
KL38-02	228	230.6	0.0018	18	0.43	0.7	92	27	7	1	2	1	0.8	1.8	8	0.01
KL38-02	230.6	233.8	0.0027	27	0.65	2.3	188	59	38	7	0.01	1	7.3	5.0	13	0.52
KL38-02	233.8	237.1	0.0053	53	0.07	9.5	2700	1670	71	2	0.01	1	8.8	8.2	11	0.21
KL38-02	237.1	242.8	0.0074	74	0.19	3.2	1070	1410	24	8	4	1	3.4	11.1	19	0.01
KL38-03	0	4	0.043	430	1	16.9	13400	12100	110	4	0.01	7	6.2	8.0	24	0.96
KL38-03	4	7	0.0083	83	0.05	0.1	250	158	13	3	0.01	3	0.4	1.6	21	0.01
KL38-03	7	10	0.0067	67	0.02	0.1	203	69	10	38	0.01	1	0.8	4.3	22	0.01
KL38-03	10	13	0.0048	48	0.11	0.1	236	78	11	1	0.01	2	0.4	1.2	24	0.01
KL38-03	13	16	0.0029	29	0.06	0.7	146	70	14	8	0.01	3	0.5	1.1	20	0.01
KL38-03	16	19	0.0064	64	0.01	0.6	81	84	20	4	0.01	2	2.4	0.6	15	0.01
KL38-03	19	22	0.0031	31	0.08	1	350	237	16	4	0.01	3	1.3	1.7	32	0.01
KL38-03	22	25	0.15	1500	0.4	5.4	8100	2200	510	15	3	2	7.3	3.8	55	0.35
KL38-03	25	29	0.104	1040	0.24	2.7	1230	550	350	10	2	4	12.8	2.3	32	0.01
KL38-03	29	33.4	0.0164	164	0.14	0.1	610	106	17	3	0.01	3	1.3	2.0	16	0.01
KL38-03	33.4	37	0.0023	23	0.04	0.8	590	216	15	2	0.01	1	2	1.0	21	0.01
KL38-03	37	40	0.0019	19	0.03	0.7	510	194	12	3	0.01	2	1	1.4	24	0.01
KL38-03	40	43	0.0026	26	0.04	0.1	1180	252	3	3	0.01	1	2.3	1.0	17	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL38-03	43	46	0.0018		18	0.04	0.6	620	150	12	1	0.01	1	1.7	1.0	18	0.01
KL38-03	46	48.8	0.0038		38	0.01	1.2	310	260	42	6	0.01	1	1.4	0.8	24	0.01
KL38-03	48.8	52	0.0107		107	0.04	0.1	402	84	12	2	0.01	1	1	1.8	17	0.01
KL38-03	52	55	0.0064		64	0.01	0.1	92	29	5	7	0.01	1	0.5	1.3	24	0.01
KL38-03	55	58	0.0023		23	0.02	0.1	318	62	10	1	0.01	1	1.3	1.2	22	0.01
KL38-03	58	61	0.037		370	0.22	11.6	3600	3200	120	4	0.01	1	24	9.0	32	0.53
KL38-03	61	64	0.04		400	0.13	0.9	153	152	47	5	2	3	2.7	3.5	27	0.01
KL38-03	64	67	0.015		150	0.13	4.3	1930	1360	62	13	7	4	9.5	4.3	29	0.18
KL38-03	67	70	0.0147		147	0.78	7.1	9600	6800	230	8	3	1	28	17.5	22	1.14
KL38-03	70	73	0.0165		165	0.27	1.4	1910	540	51	4	2	3	4.6	3.1	45	0.01
KL38-03	73	75.2	0.0046		46	0.08	0.7	510	167	28	3	1	1	2.9	3.3	35	0.01
KL38-03	75.2	79	0.056		560	0.41	1.7	1740	1280	160	23	9	3	22	12.0	70	0.46
KL38-03	79	82	0.076		760	0.79	6.2	4300	1420	260	54	82	7	12.8	16.3	84	0.01
KL38-03	82	85	0.054		540	0.24	3.6	1320	640	210	138	32	6	5.6	24.3	92	0.12
KL38-03	85	88.3	0.18		1800	0.33	48	2400	4800	200	91	307	14	12.4	61.0	70	0.1
KL38-03	88.3	91	0.38		3800	1.12	18.1	13800	4900	1260	1510	180	14	98	28.5	197	1.84
KL38-03	91	94	0.0257		257	2.32	4	11800	3400	430	1890	10	2	15.3	18.0	168	1.06
KL38-03	94	97	0.0286		286	0.39	3.7	3000	1040	64	903	21	3	6.8	8.8	64	0.1
KL38-03	97	100	0.0244		244	0.31	0.7	2400	620	60	81	1	4	2.9	4.1	305	0.1
KL38-03	100	103	0.052		520	1.42	1.4	10800	2400	340	971	2	5	12.3	7.0	65	0.46
KL38-03	103	105.7	0.0304		304	1.52	1.7	17700	4000	280	590	2	2	15.8	6.0	54	0.66
KL38-03	105.7	108.8	0.044		440	0.68	0.8	6200	1430	210	580	2	3	9	6.0	204	0.32
KL38-03	108.8	112	0.0336		336	2.24	2.1	8500	3000	300	2080	5	2	12	9.3	68	0.65
KL38-03	112	114.4	0.0091		91	1.72	2.8	10000	2300	460	2340	9	5	14	13.0	183	0.58
KL38-03	114.4	116	0.082		820	1.6	3.4	12500	1890	520	4440	26	10	18	26.0	100	0.66
KL38-03	116	118	0.0163		163	0.2	1.1	1480	160	53	165	4	2	1.9	4.2	29	0.1
KL38-03	118	121	0.0302		302	0.32	2	1960	840	51	84	7	1	3.4	10.0	21	0.12
KL38-03	121	123.4	0.052		520	0.68	23.2	44700	34600	69	71	28	4	18	120.0	34	0.76
KL38-03	123.4	126.7	0.0039		39	0.11	0.8	1020	600	25	24	1	1	1.6	2.5	21	0.01
KL38-03	126.7	129.9	0.0045		45	0.13	1	1010	520	22	24	2	1	2.5	2.8	27	0.01
KL38-03	129.9	132.8	0.0076		76	0.14	1.4	1960	750	35	22	3	1	3.8	3.3	26	0.1
KL38-03	132.8	136.1	0.0058		58	0.05	0.1	406	118	16	28	2	1	4.3	8.3	23	0.01
KL38-03	136.1	139	0.0261		261	0.2	0.7	1270	228	49	63	5	1	2	4.5	29	0.1
KL38-03	139	141.6	0.0167		167	0.12	0.8	1130	202	55	99	3	1	2.5	3.8	27	0.01
KL38-03	141.6	145	0.0305		305	0.26	1.4	1420	312	130	540	16	5	6.2	11.5	66	0.01
KL38-03	145	149	0.0289		289	1.17	3.2	1160	430	180	1840	57	10	5.2	39.0	15	0.56
KL38-03	149	152	0.0358		358	1.39	22.8	10500	6100	200	138	36	6	13.6	24.5	29	0.62
KL38-03	152	156.9	0.0357		357	0.37	5.6	6200	1410	72	84	20	3	2.5	11.8	20	0.14
KL38-03	156.9	159.5	1.1		11000	2.76	26.4	48200	1760	1720	6300	300	112	10.6	28.5	182	1.22
KL38-03	159.5	163	0.091		910	0.52	8.4	7600	1300	410	136	130	3	5.9	7.5	32	0.65
KL38-03	163	166	0.044		440	0.42	11.2	5400	1770	150	203	54	3	3.1	7.5	20	0.21
KL38-03	166	168	0.102		1020	0.39	13.4	17800	1260	180	306	94	8	3.3	22.5	34	0.28
KL38-03	168	171.1	0.32		3200	1.16	16.2	26300	540	550	528	530	22	3.6	35.5	24	0.8
KL38-03	171.1	173.2	0.47		4700	1.57	36.3	77000	1680	310	311	261	19	5.5	34.0	38	1.22
KL38-03	173.2	175	0.46		4600	1.6	10.4	7000	2500	63	415	122	34	3.6	73.0	259	0.42
KL38-03	175	178	0.525		5250	1.73	13.1	4300	78	39	132	34	34	3.1	62.0	141	0.22
KL38-03	178	181	1.01		10100	1.76	10	4700	160	48	74	32	73	3.2	19.8	87	0.26
KL38-03	181	184	0.94		9400	1.49	7.4	1170	281	280	110	29	83	3.5	55.0	183	0.36
KL38-03	184	188.2	2.16		21600	1.33	15.6	970	127	38	113	44	55	1.4	24.0	187	0.24
KL38-03	188.2	191.4	3.62		36200	0.67	13	610	342	35	62	406	120	2.9	30.0	176	0.38
KL38-03	191.4	194.2	3.28		32800	0.76	8.9	184	117	29	120	370	88	3.1	26.5	172	0.32
KL38-03	194.2	197.5	1.38		13800	0.5	4.5	640	126	210	224	27	47	2.6	17.5	224	0.62
KL38-03	197.5	199.6	2.86		28600	0.54	20.9	201	326	3380	108	82	23	8	23.0	200	2.7
KL38-03	199.6	202	1.06		10600	0.34	6.5	170	124	610	560	11	45	2.6	30.3	257	1
KL38-03	202	205	1.85		18500	0.88	7	530	188	390	140	10	101	2.2	26.5	206	1.02
KL38-03	205	208	1.1		11000	0.57	4.4	269	163	440	246	4	70	2	19.8	320	0.64
KL38-03	208	210.7	1.73		17300	0.62	5.8	190	96	280	311	5	90	1.8	29.0	249	0.88
KL38-03	210.7	213.2	1.44		14400	0.68	5.1	410	120	410	304	4	100	1.5	38.0	197	1.2
KL38-03	213.2	216.1	2.37		23700	0.66	8.7	400	137	340	421	4	70	1.7	39.0	236	1.78
KL38-03	216.1	218.1	0.443		4430	0.44	3.1	1510	134	700	646	10	56	1.4	49.0	230	0.56
KL38-03	218.1	220.1	1.06		10600	0.72	3	334	112	1710	1400	4	70	3.2	19.5	308	0.84
KL38-03	220.1	223.1	1.31		13100	0.8	3.8	530	170	200	1080	5	60	2.4	24.0	201	0.88
KL38-03	223.1	227	1.11		11100	0.96	3.7	540	195	290	354	11	70	2.8	19.3	254	0.68

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL38-03	227	230.1	1.69	16900	0.92	7.4	2300	520	330	641	80	109	3	39.5	172	0.56
KL38-03	230.1	233.5	3.29	32900	0.98	2.9	178	86	52	145	2	95	1.7	38.0	185	0.59
KL38-03	233.5	236.7	1.12	11200	0.48	1.6	630	84	32	101	4	110	1	55.0	190	0.2
KL38-03	236.7	239.3	2.09	20900	0.74	2.2	201	65	41	118	2	112	0.9	36.0	145	0.4
KL38-03	239.3	242	0.85	8500	0.54	1.4	176	62	39	37	3	73	0.8	58.0	219	0.29
KL38-03	242	245.1	1.71	17100	0.58	2.1	530	83	35	72	2	90	1.5	53.0	255	0.4
KL38-03	245.1	247.8	3.91	39100	0.68	2.8	196	56	21	64	1	89	0.8	26.0	214	0.23
KL38-03	247.8	251.5	2.82	28200	0.9	3.4	260	167	21	61	3	75	0.7	33.0	232	0.29
KL38-03	251.5	254.5	0.48	4800	0.26	1.3	580	194	35	46	4	48	0.4	37.3	152	0.12
KL38-03	254.5	257	1.5	15000	0.82	2.3	1000	260	38	69	3	80	0.4	35.5	139	0.45
KL38-03	257	260.5	1.51	15100	0.54	1.6	760	274	23	130	4	75	0.5	37.5	145	0.3
KL38-03	260.5	263.1	1.31	13100	0.56	1.9	980	235	26	399	5	57	0.4	32.0	195	0.18
KL38-03	263.1	266.4	2.48	24800	0.82	3	660	154	46	313	2	114	0.6	48.5	211	0.4
KL38-03	266.4	269.6	1.61	16100	0.55	1.6	145	46	48	167	3	106	0.7	33.0	213	0.24
KL38-03	269.6	272.5	1.15	11500	0.45	1	114	39	53	349	2	90	0.5	35.0	147	0.34
KL38-03	272.5	275.5	1.57	15700	0.56	1.9	159	74	640	500	5	145	1.8	34.0	187	0.38
KL38-03	275.5	278.5	3.77	37700	0.74	3.4	56	54	840	514	2	104	0.9	24.0	186	0.18
KL38-03	278.5	281.5	1.36	13600	0.5	1.8	148	95	410	213	5	83	3	40.0	181	0.1
KL38-03	281.5	284.5	1.17	11700	0.48	1.1	126	67	810	39	7	60	1.2	31.7	135	0.21
KL38-03	284.5	287.5	1.49	14900	0.56	4	84	44	450	38	9	82	1.1	27.5	174	0.15
KL38-03	287.5	290.5	2.49	24900	1.04	7	59	41	2080	195	8	57	3.2	22.5	72	0.11
KL38-03	290.5	293.5	2	20000	0.72	2.9	59	34	360	404	17	94	4.3	32.0	194	0.13
KL38-03	293.5	296.5	1.09	10900	0.8	2	92	56	850	329	20	90	2.3	36.0	199	0.01
KL38-03	296.5	299.5	1.49	14900	0.56	1.5	116	45	300	75	3	145	1.3	36.5	155	0.01
KL38-03	299.5	302.5	1.12	11200	2.13	3	90	56	1130	60	34	39	1.3	55.0	140	0.01
KL38-03	302.5	305.1	1.01	10100	2.05	2	105	114	1450	52	4	17	1	40.5	190	0.1
KL38-03	305.1	308.2	1.04	10400	2.61	4.3	130	129	410	15	70	11	1.2	39.5	182	0.1
KL38-03	308.2	311.3	1.38	13800	2.03	2.7	101	67	360	120	12	33	1	51.0	163	0.13
KL38-03	311.3	314.4	1.41	14100	1.73	5.4	56	40	22	30	28	75	0.5	29.0	167	0.12
KL38-03	314.4	317.8	1.25	12500	2.24	8.8	78	57	60	42	32	150	1.4	19.2	112	0.01
KL38-03	317.8	320.5	1.8	18000	1.79	5.5	94	36	63	25	29	100	0.8	30.0	143	0.01
KL38-03	320.5	323.5	1.24	12400	0.77	1.4	70	48	60	70	3	42	1.5	28.0	135	0.1
KL38-03	323.5	326.5	0.85	8500	0.5	0.8	158	50	83	125	2	28	0.8	39.0	102	0.01
KL38-03	326.5	329	1.08	10800	0.56	1.5	2800	68	65	207	6	59	0.9	76.0	120	0.1
KL38-03	329	332.5	2.53	25300	1.49	2.1	135	44	340	570	4	65	1.2	46.0	129	0.12
KL38-03	332.5	335.5	0.98	9800	1.25	0.8	40	24	21	670	5	61	0.4	79.0	97	0.01
KL38-03	335.5	338.5	0.35	3500	0.53	0.6	145	68	310	150	3	184	0.6	73.0	97	0.01
KL38-03	338.5	341.5	0.534	5340	0.85	1.5	184	113	1200	102	4	119	1	42.0	95	0.1
KL38-03	341.5	344.5	1.8	18000	1.28	2.3	374	190	2100	116	6	76	2.2	40.0	136	0.21
KL38-03	344.5	346.8	1.7	17000	1.2	2.5	226	240	1880	100	3	50	1.6	43.0	131	0.19
KL38-03	346.8	349.9	1.17	11700	0.78	1	80	84	140	70	4	40	1.1	28.5	102	0.01
KL38-03	349.9	353	1.03	10300	0.72	0.9	178	104	92	78	3	68	1.4	51.0	114	0.01
KL38-03	353	356	0.73	7300	1.44	1.8	420	98	820	117	5	58	3.3	65.0	104	0.2
KL38-03	356	359.5	0.83	8300	1.07	1.4	410	129	410	75	5	42	1.3	64.0	131	0.1
KL38-03	359.5	362.5	0.79	7900	0.69	1.1	187	53	110	50	6	45	1.4	75.0	124	0.1
KL38-03	362.5	365.5	1.42	14200	1.41	2.6	51	28	53	139	4	89	1	60.0	136	0.01
KL38-03	365.5	368.5	1.22	12200	1.07	3.3	52	35	85	93	7	50	0.6	65.0	131	0.01
KL38-03	368.5	372.5	1.48	14800	1.44	5.7	89	46	68	325	6	19	1	38.0	182	0.1
KL38-03	372.5	374.5	1.37	13700	3.28	26.7	410	124	210	284	67	41	3.8	17.0	142	0.21
KL38-03	374.5	377	1.96	19600	2.03	21	1830	104	220	360	63	33	2	27.0	103	0.2
KL38-03	377	380.2	1.77	17700	1.95	9.4	430	405	270	62	4	48	2	32.0	114	0.12
KL38-03	380.2	383.3	1.77	17700	1.68	7	314	170	530	64	8	28	1.6	27.0	96	0.1
KL38-03	383.3	386.4	1.93	19300	1.63	24.6	284	201	2150	15	46	50	1.9	28.5	85	0.01
KL38-03	386.4	390.6	1.73	17300	1.95	36.1	2010	310	3200	68	39	46	3.1	30.0	102	0.01
KL38-03	390.6	393.9	2.13	21300	1.79	23.9	510	204	4000	7	40	27	3.1	31.0	96	0.01
KL38-03	393.9	398.5	1.62	16200	1.65	27.9	5000	1470	740	168	102	17	7	37.0	85	0.01
KL38-03	398.5	401.5	1.99	19900	1.54	16.9	980	265	2100	78	46	50	2	47.5	126	0.01
KL38-03	401.5	403.5	0.65	6500	0.78	5.1	272	124	1080	233	28	24	1.9	37.5	97	0.01
KL38-03	403.5	406.8	0.313	3130	0.38	2	195	72	600	52	6	14	7.3	30.0	115	0.01
KL38-03	406.8	409.5	0.182	1820	0.2	1.2	267	271	100	103	4	13	2.9	16.5	104	0.01
KL38-03	409.5	412.5	0.33	3300	0.35	2.2	480	357	110	108	2	12	1.2	10.2	108	0.01
KL38-03	412.5	416.5	0.72	7200	0.81	3.2	310	150	760	232	7	20	1.2	13.2	127	0.1
KL38-03	416.5	419	0.466	4660	0.84	2.8	349	210	370	358	9	25	1.1	19.0	184	0.13

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL38-03	419	421.5	0.481	4810	1.4	2.5	1400	570	85	68	26	20	1.5	18.5	74	0.16
KL38-03	421.5	425.5	0.418	4180	2.32	4.2	78	42	65	95	50	14	0.8	15.2	50	0.1
KL38-03	425.5	428.5	3.35	33500	2.24	31.4	321	251	210	70	54	19	11.9	22.0	72	0.13
KL38-03	428.5	431.5	3.19	31900	2.96	24.1	670	970	30	1575	61	34	2.2	19.0	98	0.32
KL38-03	431.5	434.5	4.62	46200	2.67	31.4	1780	1540	160	650	60	30	11.2	27.5	93	0.16
KL38-03	434.5	437.5	4.83	48300	2.01	33.7	1240	1170	78	1710	56	21	8.9	31.5	76	0.2
KL38-03	437.5	440.5	3.53	35300	4.83	25.4	6200	3600	260	1050	98	79	11.6	22.0	72	0.98
KL38-03	440.5	443.5	1.27	12700	4.08	7.8	3700	1090	180	440	35	73	14.1	30.5	84	0.64
KL38-03	443.5	446.5	2.26	22600	3.84	8.1	770	314	370	225	2	110	9.3	23.0	69	0.5
KL38-03	446.5	449	2.02	20200	2.99	7.5	1230	680	850	117	5	99	10.4	31.0	44	0.26
KL38-03	449	451.5	0.88	8800	3.01	5.5	3000	760	380	25	6	83	13.4	11.5	105	0.59
KL38-03	451.5	454.3	0.433	4330	3.63	2.8	2100	280	300	3	6	51	14.2	7.2	93	0.31
KL38-03	454.3	456.5	0.34	3400	1.76	2.3	420	232	100	5	1	21	12.5	6.8	58	0.01
KL38-04	421	424	0.211	2110	0.72	1.2	58	37	22	81	15	8	0.6	8.0	42	0.01
KL38-04	424	427	0.22	2200	0.74	1.3	57	38	23	57	22	11	1	9.5	56	0.01
KL38-04	427	430	1.37	13700	2.74	18.7	104	54	62	250	42	8	1.1	17.5	72	0.2
KL38-04	430	433	2.57	25700	2.94	35.4	215	173	40	168	14	8	3.3	17.0	80	0.23
KL38-04	433	436	4.21	42100	2.16	30.2	360	340	55	130	44	16	8.2	31.3	136	0.12
KL38-04	436	439	4	40000	2.7	31.6	2390	2000	190	425	30	20	8.7	22.5	111	0.3
KL38-04	439	442	1.81	18100	4.1	11.5	1760	530	250	347	15	37	17.6	20.5	101	0.6
KL38-04	442	445.9	1.22	12200	2.5	7.8	2790	1050	240	216	5	42	10.5	10.2	65	0.4
KL38-04	445.9	449.5	0.85	8500	1.72	3.9	560	560	230	29	4	35	7	12.4	73	0.1
KL38-04	449.5	452.5	0.7	7000	2.98	6	2740	407	310	8	5	31	12.8	8.8	75	0.41
KL38-04	452.5	455.6	0.401	4010	2.42	3	1370	410	270	5	3	45	16	8.5	56	0.1
KL38-04	455.6	458.5	1.42	14200	4.1	7.4	1560	271	19	21	6	128	7.9	14.5	58	0.01
KL38-04	458.5	461.5	3.9	39000	4.78	24.7	4260	450	870	140	15	309	12.7	40.0	88	0.01
KL38-04	461.5	463.5	2.1	21000	2.24	15.6	3140	185	55	10	2	144	7.7	16.5	92	0.01
KL38-04	463.5	466.5	0.91	9100	1.62	7.6	1780	81	250	21	1	68	10.5	7.8	58	0.01
KL38-04	466.5	468	0.94	9400	1.8	8.2	1450	100	310	10	1	61	12.2	7.6	35	0.01
KL38-04	468	471	2.36	23600	2.86	11.5	1560	124	480	18	2	124	20.3	9.7	61	0.01
KL38-04	471	474	0.81	8100	0.41	5.4	293	35	120	38	6	6	14.9	1.8	35	0.01
KL38-04	474	476	0.65	6500	0.73	5.8	460	47	180	12	4	6	11.2	2.0	28	0.01
KL38-04	476	479.5	1.47	14700	2.98	7.8	340	78	360	14	9	40	30	10.5	48	0.01
KL38-04	479.5	482.5	5.53	55300	3.5	22.4	1320	221	1100	346	4	201	60	25.0	107	0.38
KL38-04	482.5	485.5	6.16	61600	5.66	22.1	3900	830	4900	635	8	149	50	57.5	142	0.4
KL38-04	485.5	488.5	0.367	3670	1.01	2.9	526	180	1120	44	18	14	11.7	8.8	40	0.01
KL38-05	0	3.9	0.0021	21	0.38	0.1	175	54	17	3	0.01	1	0.6	1.7	18	0.01
KL38-05	3.9	6.8	0.0014	14	0.19	0.1	286	97	19	3	0.01	1	1.3	2.3	20	0.01
KL38-05	6.8	8.9	0.0032	32	0.5	0.8	302	81	21	7	0.01	1	1.5	4.3	27	0.01
KL38-05	8.9	11.7	0.0025	25	0.28	0.6	357	69	9	2	0.01	1	1.3	0.8	26	0.01
KL38-05	11.7	14.7	0.0022	22	0.14	0.6	349	87	8	3	0.01	1	0.9	1.8	23	0.01
KL38-05	14.7	17.7	0.0026	26	0.29	0.7	171	72	11	2	0.01	1	0.8	1.8	21	0.01
KL38-05	17.7	20.7	0.0054	54	0.29	2.8	3320	920	26	5	0.01	1	5.1	4.0	26	0.11
KL38-05	20.7	23.5	0.0185	185	0.39	31	30200	15000	170	8	0.01	1	36	15.0	40	1.13
KL38-05	23.5	26.7	0.0024	24	0.13	0.1	241	118	13	6	0.01	1	1	1.8	21	0.01
KL38-05	26.7	29.7	0.0018	18	0.14	0.7	1360	245	14	4	0.01	1	3.1	3.0	21	0.01
KL38-05	29.7	32.7	0.0016	16	0.07	0.1	348	100	12	3	0.01	1	1.7	2.3	20	0.01
KL38-05	32.7	35.7	0.0023	23	0.08	0.8	1440	231	14	5	0.01	1	3.6	2.3	26	0.01
KL38-05	35.7	38.7	0.0045	45	0.24	2.6	2570	870	33	12	0.01	1	7.1	4.3	29	0.24
KL38-05	38.7	40.5	0.0036	36	0.13	2.2	2800	720	22	4	0.01	1	6.4	4.3	23	0.18
KL38-05	40.5	43.1	0.0038	38	0.07	0.8	650	430	66	6	0.01	1	3.8	2.5	28	0.3
KL38-05	43.1	46.2	0.0018	18	0.1	2.1	560	790	90	3	0.01	1	4.2	1.0	27	0.41
KL38-05	46.2	49	0.0009	9	0.05	0.1	430	168	6	2	0.01	1	1.6	1.3	22	0.01
KL38-05	49	53.3	0.0012	12	0.06	0.5	1260	211	4	4	0.01	1	2.3	3.8	21	0.1
KL38-05	53.3	56.7	0.0012	12	0.06	0.1	950	177	6	4	0.01	1	2.8	2.0	23	0.01
KL38-05	56.7	59.7	0.0017	17	0.08	0.6	520	95	8	3	0.01	2	2	2.5	21	0.26
KL38-05	59.7	62.7	0.0144	144	0.44	5.2	8100	2800	48	5	0.01	1	42	15.1	36	1.29
KL38-05	62.7	66	0.0083	83	1.12	2.9	13000	2600	82	7	4	1	19.7	10.3	44	0.52
KL38-05	66	68.6	0.0032	32	0.12	0.1	1680	710	26	4	2	1	3	2.8	25	0.01
KL38-05	68.6	70.5	0.0059	59	0.79	1.6	8300	2600	39	5	3	2	9.9	7.5	40	0.28
KL38-05	70.5	73.6	0.0044	44	0.37	0.7	6200	2400	23	3	1	1	5.2	5.5	32	0.2
KL38-05	73.6	76.5	0.0033	33	0.23	0.9	5000	2400	21	5	1	1	4.8	5.5	30	0.15
KL38-05	76.5	80.1	0.0167	167	0.82	1.5	7300	2700	110	37	7	5	19.5	8.3	57	0.38

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL38-05	80.1	83.3	0.0158		158	0.7	1.4	7100	2500	62	146	6	4	18.5	7.8	70	0.37
KL38-05	83.3	86.3	0.0125		125	0.22	0.7	1270	470	85	21	2	5	5.7	10.0	49	0.11
KL38-05	86.3	88.8	0.209		2090	0.36	15.3	6000	2700	540	31	176	6	86	38.5	51	0.8
KL38-05	88.8	91.6	0.5		5000	1.51	49	24800	17900	980	364	402	8	150	159.0	147	1.22
KL38-05	91.6	95.8	0.0074		74	0.91	2	7100	1390	96	351	5	2	7.8	5.3	117	0.25
KL38-05	95.8	99	0.0021		21	0.13	0.1	1970	580	30	12	1	1	3.1	2.8	94	0.01
KL38-05	99	103.1	0.0025		25	0.15	0.6	1190	356	45	34	0.01	1	2.5	1.0	126	0.01
KL38-05	103.1	107.7	0.0032		32	0.17	1.2	2830	870	55	46	1	1	4.6	2.3	131	0.01
KL38-05	107.7	110.7	0.0017		17	0.21	0.6	2200	690	44	151	3	1	4	1.8	89	0.01
KL38-05	110.7	113.7	0.199		1990	3.42	8.8	24100	2500	820	550	53	27	26	49.0	116	0.38
KL38-05	113.7	116.7	0.175		1750	0.94	4.7	19700	2100	550	108	9	13	32	24.5	93	0.41
KL38-05	116.7	119.9	0.109		1090	0.65	3.9	14800	1340	420	235	25	24	30	28.2	97	0.46
KL38-05	119.9	122.7	0.0049		49	0.1	0.7	1020	166	21	44	5	2	1.7	4.0	21	0.1
KL38-05	122.7	126.7	0.0028		28	0.28	1.2	1490	490	63	31	4	1	3.8	6.0	69	0.16
KL38-05	126.7	130.7	0.0079		79	0.25	1.8	2330	440	54	40	10	1	2.2	9.3	27	0.16
KL38-05	130.7	133.7	0.0037		37	0.07	0.7	940	195	25	53	3	1	0.9	2.0	44	0.01
KL38-05	133.7	136.3	0.0021		21	0.03	0.1	376	130	9	14	1	1	0.6	1.3	26	0.01
KL38-05	136.3	140.8	0.0045		45	0.04	0.1	460	156	11	15	2	1	0.8	2.3	31	0.01
KL38-05	140.8	142.7	0.0401		401	0.09	0.9	2420	155	130	27	34	4	2	4.3	28	0.01
KL38-05	142.7	144.7	0.0021		21	0.04	0.1	127	43	52	446	4	1	2.5	0.8	24	0.01
KL38-05	144.7	148.1	0.096		960	0.1	0.1	430	50	72	500	5	7	9.1	3.3	26	0.01
KL38-05	148.1	151.4	0.07		700	0.41	3.3	4780	390	210	179	23	13	6.2	11.0	35	0.3
KL38-05	151.4	154.8	0.0221		221	0.16	7.7	8300	920	82	32	49	40	1.7	14.5	14	0.01
KL38-05	154.8	157.2	0.0356		356	0.51	14.6	8100	4300	130	73	64	1	4.8	35.0	16	0.16
KL38-05	157.2	161	0.0351		351	0.44	13.6	9500	7400	160	54	39	1	11.3	17.0	18	0.12
KL38-05	161	164.3	0.054		540	0.23	12	4700	12100	210	107	23	1	11.1	9.0	16	0.01
KL38-05	164.3	167.1	0.0073		73	0.13	2.9	2120	2250	42	17	3	1	3	4.8	18	0.01
KL38-05	167.1	170	0.0075		75	0.08	2.5	1940	890	40	19	7	1	1.5	6.5	16	0.01
KL38-05	170	172.6	0.0094		94	0.13	4.7	3920	1280	64	16	13	1	1.5	7.5	14	0.01
KL38-05	172.6	175.1	0.0096		96	0.27	2.5	1510	550	54	34	8	1	2	4.0	30	0.14
KL38-05	175.1	178.8	0.0167		167	0.28	4.9	4010	1780	120	35	25	1	2.2	12.3	20	0.01
KL38-05	178.8	181	0.041		410	0.3	2.4	3340	376	140	54	27	6	1	2.8	26	0.01
KL38-05	181	184	0.49		4900	1.48	14.8	31500	1590	400	73	280	121	6.1	60.0	47	0.01
KL38-05	184	186.1	0.36		3600	0.88	5	490	630	57	51	37	19	9.6	11.0	26	0.01
KL38-05	186.1	188.9	0.62		6200	0.84	1.8	820	289	27	990	3	25	4.6	11.3	37	0.01
KL38-05	188.9	192	0.72		7200	1.33	2.1	530	407	16	337	7	72	3.5	15.8	39	0.01
KL38-05	192	195	0.83		8300	1.08	1.8	530	170	18	318	2	43	2.2	14.3	54	0.01
KL38-05	195	198	0.65		6500	0.74	3	710	249	16	189	2	42	0.9	12.8	40	0.01
KL38-05	198	201	0.82		8200	1.14	15.3	860	1360	26	177	2	64	2.1	29.5	35	0.01
KL38-05	201	204	1.19		11900	1.36	7.8	660	850	56	168	2	70	2.4	22.8	47	0.01
KL38-05	204	207	1.2		12000	1.31	4.9	1490	990	61	228	1	56	4	20.0	38	0.01
KL38-05	207	210	1.2		12000	1.04	13.2	256	168	64	226	11	97	1.5	28.5	44	0.01
KL38-05	210	213	1.75		17500	1.3	24	440	356	240	49	10	45	3	47.0	63	0.01
KL38-05	213	216	0.76		7600	1.06	3.6	720	232	1100	998	6	38	1.5	33.0	126	0.16
KL38-05	216	219	0.85		8500	1.2	4.5	1680	234	2280	325	7	51	1.8	32.5	98	0.32
KL38-05	219	221.7	0.31		3100	0.36	3.2	145	58	250	1580	9	17	1.5	30.6	67	0.01
KL38-05	221.7	223.2	0.34		3400	0.34	2	135	46	73	382	5	38	2.6	22.3	95	0.01
KL38-05	223.2	225.8	0.28		2800	0.21	1.5	103	40	33	79	3	28	2.7	26.5	127	0.01
KL38-05	225.8	228.4	2.21		22100	1.36	7.4	158	47	74	161	4	82	3.6	34.0	56	0.01
KL38-05	228.4	231.3	1.88		18800	1.18	5.9	152	57	63	160	3	78	7.1	26.0	38	0.01
KL38-05	231.3	234.3	1.69		16900	1.15	6.4	156	53	54	235	3	68	4.4	20.5	35	0.01
KL38-05	234.3	236.7	1.05		10500	0.91	4	189	62	62	510	2	43	6.6	15.5	42	0.01
KL38-05	236.7	239.7	0.66		6600	0.67	3.1	114	74	41	51	3	49	4.7	14.8	31	0.01
KL38-05	239.7	242.7	1.7		17000	1.03	5.2	166	57	47	342	1	54	4.9	22.0	34	0.01
KL38-05	242.7	245.7	1.5		15000	0.9	5.4	171	50	53	457	2	50	3.9	21.5	36	0.01
KL38-05	245.7	247.7	1.46		14600	0.96	6.3	1360	139	72	801	2	48	5.6	18.5	40	0.01
KL38-05	247.7	251.2	1.27		12700	0.72	1.3	361	35	13	62	5	36	0.6	22.5	31	0.01
KL38-05	251.2	254	1.62		16200	1.74	11.8	14700	407	1350	271	8	58	2	38.5	103	0.01
KL38-05	254	256.6	0.72		7200	0.64	6.1	9100	340	480	930	2	38	5.6	32.0	85	0.01
KL38-05	256.6	260.5	0.82		8200	0.48	4.6	550	70	210	53	5	56	2	40.0	138	0.01
KL38-05	260.5	264	0.59		5900	0.45	5.1	170	35	36	21	6	84	2.5	33.0	49	0.01
KL38-05	264	267	2.19		21900	1.84	12.3	106	30	38	43	15	92	1.4	53.0	131	0.01
KL38-05	267	270	1.53		15300	1.68	6.9	115	30	34	106	8	65	1.9	28.0	57	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL38-05	270	272.9	2.22	22200	1.71	14.5	134	43	11	360	8	97	2	53.0	49	0.01
KL38-05	272.9	275.7	1.96	19600	1.24	9.5	103	32	58	470	4	58	2.1	44.0	52	0.01
KL38-05	275.7	278.7	1.32	13200	1.06	4.1	66	18	24	34	5	61	0.5	39.0	63	0.01
KL38-05	278.7	281.7	1.2	12000	0.86	3.8	56	19	4	120	5	38	0.6	28.0	32	0.01
KL38-05	281.7	284.7	1.21	12100	0.78	6.2	6300	264	730	330	3	40	3.2	32.0	52	0.01
KL38-05	284.7	287.7	2.12	21200	1.66	6.3	48	21	9	25	4	69	0.7	30.0	67	0.01
KL38-05	287.7	290.7	3.43	34300	2.52	9.2	53	23	11	8	2	51	0.5	23.0	39	0.01
KL38-05	290.7	293.7	2.93	29300	1.16	5.8	420	58	1850	136	4	68	1.8	62.0	55	0.18
KL38-05	293.7	296.2	3.23	32300	1.76	5.6	133	39	250	262	2	72	1.8	33.0	51	0.33
KL38-05	296.2	299.3	2.7	27000	1.56	6.5	60	19	9	255	2	48	0.5	24.0	40	0.1
KL38-05	299.3	302.4	2.35	23500	1.36	6.3	116	37	230	340	4	40	1.8	20.0	70	0.38
KL38-05	302.4	305.5	1.88	18800	1.22	3.7	52	20	8	169	4	48	0.4	22.0	31	0.01
KL38-05	305.5	308.6	2.32	23200	1.4	5.7	56	16	8	132	3	54	0.4	27.0	40	0.01
KL38-05	308.6	311.7	4.59	45900	2.44	11.6	43	16	22	129	2	56	0.4	32.5	80	0.1
KL38-05	311.7	314.8	3.24	32400	2.72	9.6	58	28	35	177	4	60	0.8	33.0	71	0.24
KL38-05	314.8	318	5.39	53900	2.74	7.6	66	18	29	318	2	91	0.8	35.0	68	0.01
KL38-05	318	321	4.16	41600	0.96	9.8	3600	490	5200	160	3	113	9.7	71.2	70	1.91
KL38-05	321	324	5.8	58000	2.08	13.1	148	54	27	79	1	75	0.8	55.0	62	0.21
KL38-05	324	327	3.17	31700	1.86	10.1	51	15	14	104	2	53	0.5	19.0	39	0.01
KL38-05	327	330	2.33	23300	4.15	7.6	156	61	500	111	2	66	3	39.0	78	0.99
KL38-05	330	333	2.08	20800	1.04	4.2	60	67	13	48	2	46	0.7	29.0	85	0.2
KL38-05	333	336	2.38	23800	0.8	8.7	389	181	25	95	3	52	0.6	36.0	59	0.44
KL38-05	336	339	3.21	32100	1.78	7.8	420	94	640	74	2	53	1.8	20.0	56	0.38
KL38-05	339	342	4.36	43600	2.68	12.4	121	57	27	22	4	67	1.2	27.5	61	0.45
KL38-05	342	345	2.89	28900	1.82	14.1	114	81	51	17	3	54	2.4	31.0	52	0.48
KL38-05	345	347.7	3.64	36400	1.86	8.8	57	39	16	5	2	53	0.8	15.0	36	0.15
KL38-05	347.7	350.7	4.59	45900	2.24	16.1	46	38	13	9	3	58	1.1	14.5	40	0.13
KL38-05	350.7	353.7	5.17	51700	3.14	8.4	33	17	11	48	3	65	0.7	32.5	94	0.01
KL38-05	353.7	356.7	3.69	36900	4.5	16.6	59	180	770	60	4	55	0.9	26.0	72	0.59
KL38-05	356.7	359.7	3.66	36600	3.5	23.2	78	49	820	78	4	66	0.9	21.0	70	0.35
KL38-05	359.7	362.7	3.61	36100	4.7	16.4	44	21	61	91	4	68	0.7	21.0	84	0.01
KL38-05	362.7	365.7	4.16	41600	3.82	9.8	98	570	2000	33	2	53	2.2	27.0	85	0.24
KL38-05	365.7	368.7	4.99	49900	4.2	13.5	239	1120	1680	49	2	54	4.2	30.0	78	0.47
KL38-05	368.7	371.7	5.56	55600	4.74	16.5	510	1800	3600	45	3	43	3.2	42.5	51	0.45
KL38-05	371.7	374.8	4.3	43000	3.46	15.7	59	34	22	8	3	38	1	20.5	39	0.01
KL38-05	374.8	377.8	2.9	29000	2.04	10.4	57	20	11	8	7	47	0.9	28.0	47	0.01
KL38-05	377.8	380.8	3.65	36500	2.52	17.9	510	23	15	7	11	95	1.2	13.5	88	0.01
KL38-05	380.8	383.8	3.25	32500	2.54	17	710	34	14	6	10	63	1.3	12.0	72	0.01
KL38-05	383.8	386.9	2.13	21300	1.82	15.3	361	44	10	11	7	48	1.1	14.0	94	0.15
KL38-05	386.9	389.7	2.97	29700	2.24	18.4	1760	89	10	10	8	67	1.5	17.0	54	0.01
KL38-05	389.7	392.7	2.3	23000	1.98	9.3	550	29	7	51	7	55	1.4	23.0	102	0.01
KL38-05	392.7	395.7	1.6	16000	1.5	11.7	440	126	41	18	5	26	1.2	14.5	114	0.01
KL38-05	395.7	398.7	2.36	23600	1.76	15.1	450	323	350	49	5	23	1.8	14.0	196	0.01
KL38-05	398.7	401.7	1.44	14400	1.5	16.5	1310	520	240	42	8	28	1.9	10.0	152	0.01
KL38-05	401.7	404.7	1.1	11000	1.08	18	470	90	21	39	7	30	1.7	12.0	208	0.01
KL38-05	404.7	407.7	1.93	19300	1.48	15.5	1070	69	9	20	10	62	1.9	16.0	97	0.01
KL38-05	407.7	410.7	1.94	19400	0.94	7.4	950	66	13	11	12	92	2.3	13.5	52	0.01
KL38-05	410.7	413.7	1.74	17400	0.78	7.3	940	81	12	10	5	86	1.6	15.5	65	0.01
KL38-05	413.7	416.8	2	20000	0.96	6.4	1340	166	17	28	7	175	1.7	12.0	56	0.01
KL38-05	416.8	419.9	1.38	13800	0.94	6.2	630	94	21	71	7	107	2.6	24.5	64	0.01
KL38-05	419.9	422.9	0.835	8350	0.68	3.7	510	114	10	22	13	72	1.6	10.9	57	0.01
KL38-05	422.9	425.9	1.66	16600	0.92	6.5	720	69	4	9	6	125	1.1	18.5	55	0.01
KL38-05	425.9	429	2.5	25000	0.98	10.5	1040	164	2	16	8	68	0.4	4.0	26	0.01
KL38-05	429	432	1.96	19600	1.2	11.4	375	72	16	71	14	66	0.6	13.3	103	0.26
KL38-05	432	435	0.6	6000	0.88	3.5	1530	299	280	494	6	17	0.6	11.8	107	0.84
KL38-05	435	438	0.81	8100	0.46	2.6	391	129	1350	2010	3	20	33	9.5	96	0.25
KL38-05	438	441	1.03	10300	0.5	5.7	520	196	65	920	6	33	2	16.0	89	0.16
KL38-05	441	444	0.75	7500	0.5	6.1	720	420	2100	450	4	16	14.8	9.8	84	0.42
KL38-05	444	447	0.74	7400	0.22	3.7	412	161	43	96	5	15	1.5	13.0	76	0.11
KL38-05	447	450	0.445	4450	0.28	3.1	261	206	380	58	5	13	1.1	16.3	66	0.26
KL38-05	450	452.1	0.64	6400	0.28	5	378	191	1190	75	3	21	4.8	11.5	112	0.33
KL38-05	452.1	454.8	0.82	8200	0.68	3.6	440	204	53	80	17	15	1.6	11.5	117	0.2
KL38-05	454.8	457	0.58	5800	0.32	2	132	84	22	124	2	16	0.6	7.6	60	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL38-05	457	459.7	1.25	12500	1.3	14.1	1130	287	87	6	34	47	2.2	11.5	157	0.6
KL38-05	459.7	462	2.15	21500	1.54	15.3	1120	260	150	58	24	38	2.8	19.0	159	1
KL38-05	462	464.9	1.28	12800	1.08	17.8	190	263	24	69	22	27	1.4	10.5	181	0.12
KL38-05	464.9	467.9	2.33	23300	1.82	22.9	650	245	18	20	2	19	1.2	28.0	183	0.17
KL38-05	467.9	470.7	1.57	15700	1.18	35.1	333	182	16	66	38	21	1.3	13.7	179	0.01
KL38-05	470.7	473.7	1.2	12000	1.18	28.4	500	275	53	37	26	24	1.4	18.5	192	0.01
KL38-05	473.7	476.4	1.47	14700	1.62	24.8	2600	480	180	60	10	23	2.4	20.3	151	0.01
KL38-05	476.4	479.4	2.02	20200	3	12.2	13900	3400	190	7	7	37	1.5	20.0	68	0.19
KL38-05	479.4	482.5	3.8	38000	4.2	8	1490	1120	10	5	3	51	1	21.0	54	0.01
KL38-05	482.5	485.6	3.18	31800	3.66	5.9	2150	4000	12	26	4	54	1.5	19.0	56	0.01
KL38-05	485.6	488.7	3.46	34600	3.42	5.1	1480	337	18	2	2	40	1.1	30.0	52	0.01
KL38-05	488.7	491.7	2.44	24400	2.89	3.6	880	196	18	3	2	28	0.8	27.0	38	0.01
KL38-05	491.7	494.7	3.35	33500	3.62	4.4	910	123	10	3	2	49	0.8	25.5	52	0.01
KL38-05	494.7	497.7	2.7	27000	3.62	3.5	540	55	0.01	1	2	43	0.4	13.0	39	0.01
KL38-05	497.7	500.7	3	30000	3.82	4	480	54	0.01	1	2	42	0.9	0.0	30	0.01
KL38-05	500.7	503.7	2.76	27600	3.14	4	325	69	3	3	3	50	0.4	10.0	42	0.01
KL38-05	503.7	506.1	2.81	28100	2.52	4.6	710	127	4	4	3	50	1.1	8.0	46	0.01
KL38-05	506.1	508.2	2.01	20100	1.64	3.9	790	84	4	4	2	64	0.5	7.5	36	0.01
KL38-05	508.2	510.4	0.77	7700	0.7	4.1	480	181	39	42	28	43	0.8	15.3	42	0.01
KL38-05	510.4	512.7	0.62	6200	0.86	3.5	293	82	40	9	15	65	0.5	20.0	91	0.01
KL38-05	512.7	515.7	1.26	12600	1.48	6.4	730	74	29	14	14	58	0.6	21.4	31	0.01
KL38-05	515.7	518.7	1.75	17500	1.36	5.3	860	27	14	1	5	44	0.3	11.5	54	0.01
KL38-05	518.7	521.7	1.59	15900	1.15	4.5	550	28	17	3	4	60	0.3	18.0	41	0.01
KL38-05	521.7	524.7	1.6	16000	1.02	3.2	406	18	27	60	4	69	0.3	15.0	29	0.01
KL38-05	524.7	527.7	1.09	10900	0.82	4.5	359	26	41	9	13	49	0.5	23.0	30	0.01
KL38-05	527.7	530.7	1.48	14800	1.4	10.5	179	23	32	15	16	51	1	17.5	62	0.01
KL38-05	530.7	533.7	1.67	16700	1.88	6.6	580	31	44	5	69	38	0.4	23.7	55	0.01
KL38-05	533.7	536.7	0.62	6200	0.53	1.9	53	13	39	7	174	10	0.3	41.3	66	0.01
KL38-05	536.7	539.7	0.87	8700	0.95	3.3	64	11	23	6	103	10	0.8	29.5	83	0.01
KL38-05	539.7	542.7	0.85	8500	0.68	2.8	86	29	20	412	6	15	0.4	15.5	67	0.01
KL38-05	542.7	545.7	1.45	14500	0.88	3.3	271	29	6	113	0.01	15	0.2	10.0	27	0.01
KL38-05	545.7	548.7	1.25	12500	0.73	2.5	170	17	8	75	1	19	0.4	9.6	19	0.01
KL38-05	548.7	551.7	1.08	10800	0.73	2.3	240	37	12	18	2	16	0.9	9.4	31	0.01
KL38-05	551.7	554.7	0.68	6800	0.45	1.5	155	11	11	8	4	19	0.6	9.8	24	0.01
KL38-05	554.7	557.7	0.46	4600	0.31	1	79	20	14	376	3	21	0.5	15.8	38	0.01
KL38-05	557.7	560.7	1.3	13000	0.42	2.4	42	9	15	124	0.01	28	0.4	12.5	37	0.01
KL38-05	560.7	563.7	0.95	9500	0.61	2.1	53	11	12	38	4	26	0.5	19.5	54	0.01
KL38-05	563.7	566.7	1.08	10800	0.57	2.3	65	12	8	16	2	33	0.3	12.0	40	0.01
KL38-05	566.7	569.7	0.501	5010	0.33	1.2	64	11	7	81	1	24	3.6	16.0	43	0.01
KL38-05	569.7	572.7	1.2	12000	0.91	5.9	152	11	19	38	1	26	8.9	12.5	54	0.01
KL38-05	572.7	575.7	0.348	3480	0.13	0.7	52	13	2	70	1	24	0.01	21.0	46	0.01
KL38-05	575.7	578.7	0.467	4670	0.36	3.8	350	20	11	40	7	10	0.3	8.0	26	0.01
KL38-05	578.7	581.7	1.26	12600	0.77	4.3	141	7	4	26	2	36	0.6	18.5	28	0.01
KL38-05	581.7	584.7	1.02	10200	0.56	2.2	53	8	9	408	1	44	0.01	14.6	50	0.01
KL38-05	584.7	587.7	1.62	16200	0.53	3.1	50	6	9	130	2	49	0.01	26.0	75	0.01
KL38-05	587.7	590.7	0.96	9600	0.48	2.3	64	18	11	596	3	28	0.01	22.0	40	0.01
KL38-05	590.7	593.7	1.07	10700	0.6	3	71	8	10	71	1	19	0.8	9.9	37	0.01
KL38-05	593.7	596.7	0.99	9900	0.35	2	33	10	6	1350	2	19	0.01	17.8	57	0.01
KL38-05	596.7	599.7	0.534	5340	0.27	1.6	45	16	5	39	2	20	0.01	22.7	53	0.01
KL38-05	599.7	602.7	1.07	10700	0.56	3.1	81	8	8	125	0.01	29	0.01	14.0	23	0.01
KL38-05	602.7	605.7	1.02	10200	0.6	2.5	65	7	5	47	1	37	0.01	17.0	40	0.01
KL38-05	605.7	608.7	0.87	8700	0.49	1.8	79	13	2	26	0.01	27	0.01	9.1	25	0.01
KL38-05	608.7	611.7	0.542	5420	0.28	1.3	51	7	7	36	1	15	0.01	11.3	25	0.01
KL38-05	611.7	614.7	0.67	6700	0.39	1.9	62	6	16	10	1	17	0.8	8.3	27	0.01
KL38-05	614.7	617.7	0.418	4180	0.27	1.3	70	7	12	36	1	9	2.7	5.8	14	0.01
KL38-05	617.7	620.7	0.94	9400	0.6	3	72	8	16	20	2	31	1.4	10.5	34	0.01
KL38-05	620.7	623.7	1.06	10600	0.57	3.3	90	8	4	77	2	29	0.01	7.8	42	0.01
KL38-05	623.7	626.7	1.17	11700	1	5.4	5300	2500	69	50	1	27	0.5	9.0	28	0.18
KL38-05	626.7	629.7	1.16	11600	0.35	1.7	75	21	6	156	1	27	0.01	26.5	74	0.01
KL38-05	629.7	632.7	1.4	14000	0.93	12.4	304	11	18	55	2	25	0.01	19.5	34	0.01
KL38-05	632.7	635.7	0.341	3410	0.14	0.9	42	6	3	40	0.01	11	0.01	7.8	22	0.01
KL38-05	635.7	638.7	0.24	2400	0.06	0.7	38	6	2	1040	0.01	7	0.01	4.3	15	0.01
KL38-05	638.7	641.7	0.157	1570	0.03	0.6	32	5	2	157	0.01	5	0.01	5.8	27	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL38-05	641.7	644.7	0.347	3470	0.15	2.1	79	10	5	518	1	12	0.2	6.3	17	0.01
KL38-05	644.7	647.7	0.485	4850	0.28	2.5	119	17	3	26	0.01	11	0.5	6.3	18	0.01
KL38-05	647.7	650.7	0.231	2310	0.13	1.3	56	13	4	75	0.01	10	0.2	4.8	9	0.01
KL38-05	650.7	653.7	0.396	3960	0.37	1.7	170	112	5	40	2	16	0.4	13.5	31	0.01
KL38-05	653.7	656.7	0.487	4870	0.25	7.2	4030	1010	6	16	22	12	0.6	13.0	31	0.01
KL38-05	656.7	659.7	0.169	1690	0.08	1.4	69	20	4	44	0.01	4	0.2	12.0	34	0.01
KL38-05	659.7	662.7	0.356	3560	0.22	1.2	63	8	1	34	2	7	0.01	5.6	34	0.01
KL38-05	662.7	665.7	0.491	4910	0.37	1.9	51	9	6	40	1	9	0.01	9.8	46	0.01
KL38-05	665.7	668.7	0.26	2600	0.25	1.3	43	10	4	21	0.01	9	0.5	4.8	24	0.01
KL38-05	668.7	671.7	0.44	4400	0.35	1.7	50	12	2	53	0.01	13	0.2	13.5	52	0.01
KL38-05	671.7	674.7	0.73	7300	0.98	1.4	97	9	2	10	1	17	0.01	21.5	60	0.01
KL38-05	674.7	677.7	0.21	2100	0.19	0.1	47	6	1	27	0.01	8	0.01	6.5	35	0.01
KL38-05	677.7	680.7	0.415	4150	0.17	1	63	14	5	366	0.01	11	0.01	21.2	55	0.01
KL38-05	680.7	683.7	0.506	5060	0.41	0.8	65	8	2	22	0.01	12	0.01	7.3	42	0.01
KL38-05	683.7	686.7	2.16	21600	1.61	3.2	173	8	2	12	0.01	32	0.2	19.0	48	0.01
KL38-05	686.7	689.7	1.7	17000	1.21	2.7	135	6	1	26	0.01	25	0.01	16.5	41	0.01
KL38-05	689.7	692.7	0.57	5700	0.75	0.7	56	6	1	40	0.01	7	0.01	5.8	32	0.01
KL38-05	692.7	695.7	0.72	7200	0.73	1	93	7	1	21	0.01	10	0.2	7.3	46	0.01
KL38-05	695.7	698.7	0.51	5100	0.36	0.9	71	6	4	53	0.01	9	0.2	7.0	41	0.01
KL38-05	698.7	701.7	0.529	5290	0.33	1.2	96	6	10	13	1	14	0.01	6.0	37	0.01
KL38-05	701.7	704.7	0.54	5400	0.17	2.3	140	16	9	14	1	14	0.2	6.8	44	0.01
KL38-05	704.7	706	0.434	4340	0.19	2.6	173	23	7	40	4	11	0.4	4.5	38	0.01
KL38-05	706	709	0.25	2500	0.11	3.7	112	59	8	19	18	5	0.5	10.8	35	0.01
KL38-05	709	712.4	0.259	2590	0.11	2	62	15	16	24	1	5	0.3	5.5	40	0.01
KL38-05	712.4	714.5	0.231	2310	0.09	1	52	7	7	82	0.01	8	0.3	3.3	103	0.01
KL38-05	714.5	717.4	1.68	16800	0.56	3.6	163	17	11	470	0.01	36	0.2	20.5	63	0.01
KL38-05	717.4	720	0.164	1640	0.04	0.1	39	9	7	115	1	5	0.4	6.3	30	0.01
KL38-05	720	722.4	0.46	4600	0.17	3.4	122	20	11	89	2	8	0.5	5.3	50	0.24
KL38-05	722.4	725.5	0.0291	291	0.01	0.1	37	7	9	17	0.01	1	0.2	1.0	12	0.11
KL38-05	725.5	728.6	0.182	1820	0.05	0.7	69	30	25	102	0.01	6	0.3	7.3	119	0.27
KL38-05	728.6	731.7	0.163	1630	0.05	0.6	64	8	18	129	0.01	5	0.8	3.8	171	0.35
KL38-05	731.7	734.7	0.276	2760	0.1	1.2	120	31	17	63	0.01	7	0.2	7.0	123	0.26
KL38-05	734.7	737.7	0.55	5500	0.18	1.9	102	34	24	80	3	17	0.6	13.4	62	0.01
KL38-05	737.7	740.7	0.221	2210	0.07	1.1	32	8	6	46	0.01	7	0.2	4.5	69	0.01
KL38-05	740.7	743.7	0.433	4330	0.15	1.9	68	39	4	26	2	8	0.8	10.5	33	0.01
KL38-05	743.7	746.7	0.162	1620	0.04	0.6	27	6	3	24	1	6	0.5	4.8	28	0.01
KL38-05	746.7	749.7	0.107	1070	0.04	0.1	22	5	2	29	0.01	7	0.2	6.5	29	0.01
KL38-05	749.7	752.7	0.091	910	0.02	0.1	25	6	4	148	0.01	3	0.2	2.8	42	0.01
KL38-05	752.7	755.7	1	10000	0.41	1.4	83	6	2	90	0.01	11	0.2	7.5	20	0.01
KL38-05	755.7	758.7	1.23	12300	0.36	2.7	111	22	1	58	0.01	18	1.3	11.0	31	0.01
KL38-05	758.7	760.8	0.129	1290	0.05	0.1	29	10	1	98	0.01	5	0.7	2.5	20	0.01
KL38-05	760.8	762.6	0.121	1210	0.04	0.1	22	1	1	24	0.01	4	0.2	3.3	10	0.01
KL38-05	762.6	764.7	0.85	8500	0.31	2.5	90	6	2	129	0.01	50	0.4	18.0	43	0.01
KL38-05	764.7	767.7	2.15	21500	0.64	5.7	100	6	2	248	0.01	67	0.3	31.0	53	0.01
KL38-05	767.7	770.7	0.84	8400	0.32	2.3	78	5	3	127	0.01	28	0.01	21.3	37	0.01
KL38-05	770.7	773.7	0.98	9800	0.44	2.2	98	6	2	28	0.01	18	0.6	8.5	54	0.01
KL38-05	773.7	775.7	1.16	11600	0.59	3.2	112	22	3	74	0.01	31	0.8	20.0	46	0.01
KL38-05	775.7	778.4	2.34	23400	1.8	5.2	206	9	0.01	24	0.01	51	1.1	18.0	30	0.01
KL38-05	778.4	780.8	0.375	3750	0.16	1.1	93	8	9	48	0.01	17	2.5	9.5	36	0.01
KL38-05	780.8	782.7	1.04	10400	0.6	4	150	14	9	8	1	15	0.7	14.8	27	0.01
KL38-05	782.7	785.7	0.54	5400	0.25	2.2	142	11	7	46	0.01	29	0.7	24.2	30	0.01
KL38-05	785.7	788.7	0.489	4890	0.24	2.3	152	8	12	174	1	12	0.8	12.8	35	0.01
KL38-05	788.7	791.7	0.66	6600	0.35	3.6	164	10	13	33	0.01	26	4	9.8	48	0.01
KL38-05	791.7	794.7	0.59	5900	0.37	2.9	116	9	8	149	1	32	0.4	21.0	52	0.01
KL38-05	794.7	797.8	0.97	9700	0.57	4.8	182	8	10	50	1	36	0.01	17.9	40	0.01
KL38-05	797.8	800.9	0.39	3900	0.21	2.3	188	11	15	10	1	11	0.7	12.0	37	0.01
KL38-05	800.9	803.9	0.54	5400	0.32	4.7	401	11	10	8	1	10	0.4	8.5	28	0.01
KL38-05	803.9	806.9	0.498	4980	0.28	3.2	600	44	6	14	1	10	0.7	6.0	20	0.01
KL38-05	806.9	809.7	0.83	8300	0.55	4.6	500	22	16	27	1	12	1.2	9.5	18	0.01
KL38-05	809.7	812.7	0.121	1210	0.11	1.1	177	17	8	6	1	5	0.01	3.8	10	0.01
KL38-05	812.7	815.7	0.128	1280	0.1	1.4	153	17	4	9	0.01	3	0.01	3.3	8	0.01
KL38-05	815.7	818.7	0.7	7000	0.44	3.5	223	12	13	24	1	14	0.01	9.9	26	0.01
KL38-05	818.7	821.7	0.8	8000	0.45	3.8	305	8	14	11	1	12	0.01	7.0	19	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL38-05	821.7	824.7	1.15	11500	0.51	5	280	7	7	300	1	38	0.01	13.6	21	0.01
KL38-05	824.7	827.8	0.396	3960	0.22	2.6	271	13	7	30	1	12	0.3	5.0	16	0.01
KL38-05	827.8	830.8	0.156	1560	0.08	0.7	250	37	8	35	4	4	0.4	4.8	18	0.01
KL38-05	830.8	833.9	0.22	2200	0.1	0.8	195	17	9	7	2	6	0.01	4.1	16	0.01
KL38-05	833.9	837	0.512	5120	0.33	2.8	400	18	5	4	8	9	0.01	8.4	30	0.01
KL38-05	837	840	0.329	3290	0.13	2.8	295	28	15	8	14	7	0.01	3.9	20	0.01
KL38-05	840	843	0.498	4980	0.3	2.3	238	20	8	8	2	14	0.01	8.0	28	0.01
KL38-05	843	846.1	0.521	5210	0.32	2.5	356	23	15	24	1	12	0.01	7.0	29	0.01
KL38-05	846.1	849.5	0.536	5360	0.27	3	300	20	18	18	1	10	0.4	6.0	21	0.01
KL38-05	849.5	851.7	0.309	3090	0.17	2.4	1680	1340	23	16	1	4	0.3	3.8	16	0.01
KL38-05	851.7	853.7	0.135	1350	0.07	0.8	188	29	10	12	0.01	3	0.01	2.3	15	0.01
KL38-05	853.7	856.9	0.209	2090	0.1	1.2	221	47	10	14	1	4	1.3	4.8	20	0.01
KL38-05	856.9	859.9	0.22	2200	0.15	1.8	140	12	8	10	1	3	0.01	2.3	15	0.01
KL38-05	859.9	862.2	0.26	2600	0.16	1.3	152	37	21	12	1	4	0.01	2.6	16	0.01
KL38-05	862.2	865.3	0.25	2500	0.13	1.8	126	16	4	15	1	5	0.01	3.3	20	0.01
KL38-05	865.3	868.7	0.059	590	0.03	0.1	117	18	3	6	0.01	4	0.01	1.4	17	0.01
KL38-05	868.7	870.5	0.068	680	0.04	0.6	85	48	3	23	3	2	0.01	2.3	14	0.01
KL38-05	870.5	873.4	0.131	1310	0.21	1.4	127	25	4	11	4	3	0.01	3.5	15	0.01
KL38-05	873.4	876.4	0.127	1270	0.15	1	108	22	4	20	3	4	0.01	2.0	18	0.01
KL38-05	876.4	880.4	0.453	4530	0.74	4	295	14	10	57	5	8	0.01	4.4	22	0.01
KL38-05	880.4	883.5	0.16	1600	0.2	1.5	135	18	8	44	28	3	0.01	5.8	17	0.01
KL38-05	883.5	886.7	0.059	590	0.06	0.6	68	15	7	36	14	3	0.01	3.3	13	0.01
KL38-05	886.7	890.4	0.123	1230	0.17	0.9	98	14	6	129	6	2	0.01	3.5	10	0.01
KL38-05	890.4	893.7	0.449	4490	0.52	4	245	41	30	870	18	9	0.3	11.7	29	0.01
KL38-05	893.7	896.7	0.057	570	0.18	0.1	32	11	15	277	6	4	0.3	1.9	10	0.01
KL38-05	896.7	899.7	0.0081	81	0.02	0.1	37	15	18	41	0.01	4	0.4	0.0	18	0.01
KL38-05	899.7	902.7	0.26	2600	0.08	1.8	65	10	6	47	5	4	0.3	2.0	8	0.01
KL38-05	902.7	905.7	0.22	2200	0.12	1.3	36	11	11	200	7	5	0.01	1.5	10	0.01
KL38-05	905.7	908.7	0.24	2400	0.25	1.1	26	11	14	135	4	9	0.3	2.4	10	0.01
KL38-05	908.7	911.7	0.25	2500	0.36	1.6	90	10	11	570	5	10	0.5	2.3	16	0.01
KL38-05	911.7	914.7	0.14	1400	0.15	1.4	35	9	11	56	2	7	0.5	2.0	10	0.01
KL38-05	914.7	917.7	0.453	4530	0.89	3.2	201	13	10	47	3	22	0.3	4.8	20	0.01
KL38-05	917.7	920.7	1.75	17500	3.63	11	940	12	15	16	2	84	0.01	14.0	28	0.01
KL38-05	920.7	923.7	0.173	1730	0.24	1.1	80	7	9	261	2	6	0.3	2.1	10	0.01
KL38-05	923.7	926.7	0.063	630	0.17	0.1	430	14	21	28	5	10	0.3	2.1	12	0.01
KL38-05	926.7	929.3	0.0157	157	0.02	0.1	1050	11	18	7	3	3	0.01	0.8	17	0.01
KL38-05	929.3	931	0.0072	72	0.01	0.1	24	10	12	8	3	1	0.01	0.0	19	0.01
KL38-05	931	933.2	0.0145	145	0.03	0.1	81	13	12	7	0.01	1	0.3	1.0	12	0.01
KL38-05	933.2	935.7	0.0147	147	0.06	0.1	101	11	13	10	2	1	0.01	0.9	16	0.01
KL38-05	935.7	938.2	0.089	890	0.11	0.1	84	13	8	80	4	2	0.3	2.0	12	0.01
KL38-05	938.2	941.7	0.083	830	0.09	0.1	76	12	10	20	5	2	0.01	2.3	16	0.01
KL38-05	941.7	944.7	0.0059	59	0.01	0.1	80	9	6	7	0.01	1	0.01	0.0	20	0.01
KL38-05	944.7	947.7	0.0038	38	0.01	0.1	11	11	6	4	1	1	0.01	0.0	12	0.01
KL38-05	947.7	950.7	0.0059	59	0.01	0.1	47	42	10	4	3	1	0.01	0.0	17	0.01
KL38-05	950.7	953.7	0.0152	152	0.02	0.1	28	11	9	6	4	1	0.01	1.4	16	0.01
KL38-05	953.7	957	0.0101	101	0.02	0.1	66	13	8	4	1	1	0.01	0.9	14	0.01
KL38-05	957	961	0.151	1510	0.4	2	164	12	13	87	36	5	0.01	2.0	16	0.01
KL38-05	961	964	0.071	710	0.13	0.9	123	9	11	15	6	5	0.01	2.3	22	0.01
KL38-05	964	969.4	0.023	230	0.04	0.1	30	12	6	7	5	2	0.01	1.2	17	0.01
KL38-05	969.4	973.8	0.0296	296	0.06	0.1	111	25	19	25	16	2	0.01	2.8	16	0.01
KL38-05	973.8	975.7	0.071	710	0.15	0.8	440	16	21	114	47	3	0.01	2.8	14	0.01
KL38-05	975.7	978.8	0.0252	252	0.04	0.1	41	12	15	16	4	1	0.01	1.5	12	0.01
KL38-05	978.8	981.9	0.059	590	0.03	0.5	85	17	23	6	6	1	0.01	1.6	10	0.01
KL38-05	981.9	985.2	0.0118	118	0.02	0.1	40	54	37	10	32	3	0.01	5.9	12	0.01
KL38-05	985.2	988.2	0.074	740	0.13	1.3	392	91	8	64	4	10	0.01	2.8	8	0.01
KL38-05	988.2	990.5	0.0242	242	0.02	0.1	101	19	23	13	5	2	0.01	1.4	6	0.01
KL38-05	990.5	993.5	0.0061	61	0.01	0.1	68	17	10	15	6	4	0.01	1.4	10	0.01
KL38-05	993.5	996.6	0.0061	61	0.01	0.1	71	15	11	12	5	3	0.01	1.1	6	0.01
KL38-05	996.6	999.7	0.0039	39	0.01	0.1	30	17	9	6	2	1	0.01	1.0	5	0.01
KL38-05	999.7	1001.7	0.0036	36	0.01	0.1	133	25	8	4	1	1	0.01	0.8	7	0.01
KL38-05	1001.7	1004.7	0.008	80	0.01	0.1	104	23	8	5	1	1	0.01	0.7	7	0.01
KL38-05	1004.7	1007.7	0.0148	148	0.01	0.1	71	20	16	7	2	1	0.01	0.7	10	0.01
KL38-05	1007.7	1010.7	0.0081	81	0.01	0.1	35	14	7	6	3	1	0.01	2.1	8	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL38-05	1010.7	1013.7	0.0032		32	0.01	0.1	24	9	5	7	2	1	0.01	1.0	13	0.01
KL38-05	1013.7	1016.7	0.0031		31	0.01	0.1	25	22	5	5	2	1	0.01	0.5	6	0.01
KL38-05	1016.7	1019.7	0.0036		36	0.01	0.1	62	25	12	7	2	1	0.01	2.1	7	0.01
KL38-05	1019.7	1022.7	0.0181		181	0.02	0.1	111	67	30	20	3	4	0.4	3.3	11	0.01
KL38-05	1022.7	1025.7	0.0226		226	0.02	0.1	110	39	19	18	3	4	0.5	1.3	7	0.01
KL38-05	1025.7	1028.7	0.047		470	0.07	0.1	115	31	21	13	2	3	0.3	1.6	12	0.01
KL38-05	1028.7	1031.7	0.049		490	0.05	0.1	110	30	28	17	2	3	0.01	1.2	10	0.01
KL38-06	0	4.5	0.0087		87	0.62	0.7	560	161	26	3	0.01	1	1	0.8	20	0.01
KL38-06	4.5	13.6	0.0134		134	0.24	0.5	320	106	33	3	0.01	1	0.6	0.8	19	0.01
KL38-06	13.6	18	0.0027		27	0.01	0.1	141	105	20	2	0.01	1	0.5	0.7	21	0.01
KL38-06	18	21	0.0202		202	0.06	0.6	540	178	10	1	0.01	1	1.2	0.5	22	0.01
KL38-06	21	24	0.0082		82	0.01	0.5	460	171	10	1	0.01	2	0.8	0.0	27	0.01
KL38-06	24	27	0.0112		112	0.01	0.1	327	119	9	1	0.01	1	0.9	0.8	26	0.01
KL38-06	27	30	0.0061		61	0.08	0.9	1490	550	11	1	0.01	1	2.7	0.7	30	0.01
KL38-06	30	33.4	0.0073		73	0.08	0.1	420	169	22	13	2	4	2.2	1.6	28	0.01
KL38-06	33.4	35.2	0.0082		82	0.01	0.7	232	236	12	5	0.01	1	1.2	0.9	25	0.01
KL38-06	35.2	38.2	0.0223		223	0.04	0.7	420	193	15	3	0.01	2	1.4	0.9	23	0.01
KL38-06	38.2	41.5	0.0105		105	0.12	0.5	1260	540	13	4	0.01	1	3.4	1.4	17	0.01
KL38-06	41.5	44.6	0.007		70	0.1	0.6	1120	376	11	4	0.01	1	2.4	1.3	19	0.01
KL38-06	44.6	47.7	0.0039		39	0.04	0.5	800	246	12	5	0.01	2	1.6	1.3	22	0.01
KL38-06	47.7	50.7	0.0032		32	0.06	0.1	760	281	8	2	0.01	1	1.5	1.0	16	0.01
KL38-06	50.7	54	0.0044		44	0.3	0.7	2480	590	27	3	0.01	1	3.5	1.6	20	0.15
KL38-06	54	57	0.0019		19	0.1	0.1	1200	324	12	3	0.01	1	2.2	1.4	19	0.11
KL38-06	57	60.2	0.0014		14	0.02	0.1	720	242	6	2	0.01	1	1.5	1.9	18	0.1
KL38-06	60.2	63.2	0.001		10	0.01	0.1	91	30	5	3	0.01	1	0.6	0.9	20	0.01
KL38-06	63.2	66.2	0.0011		11	0.01	0.1	223	63	2	1	0.01	1	0.9	0.8	15	0.01
KL38-06	66.2	69.2	0.0014		14	0.04	0.1	114	34	18	2	0.01	1	0.8	0.9	25	0.01
KL38-06	69.2	72.2	0.058		580	0.57	31.2	19400	11000	350	3	2	1	130	15.6	28	1.98
KL38-06	72.2	75.2	0.0048		48	0.24	0.1	287	102	12	2	0.01	3	1.5	1.9	20	0.18
KL38-06	75.2	78.2	0.0031		31	0.04	0.1	367	109	32	6	3	3	2.1	1.4	30	0.13
KL38-06	78.2	82.1	0.0015		15	0.02	0.1	143	57	16	1	0.01	1	0.8	1.1	20	0.01
KL38-06	82.1	84	0.0084		84	0.02	0.1	460	164	17	5	0.01	1	1.3	1.5	21	0.14
KL38-06	84	87	0.0375		375	0.06	0.1	381	147	160	1	4	4	5.1	2.2	25	0.19
KL38-06	87	90	0.0097		97	0.22	0.7	510	223	150	31	7	4	6.1	3.4	68	0.17
KL38-06	90	93	0.0323		323	0.23	1.6	2760	640	140	233	10	4	4.1	3.6	38	0.21
KL38-06	93	96	0.04		400	0.06	0.8	1460	342	140	38	22	3	5.8	2.2	35	0.2
KL38-06	96	98.9	0.016		160	0.14	0.9	780	306	150	39	35	1	6.7	12.3	108	0.13
KL38-06	98.9	102	0.0084		84	0.27	1.5	480	236	120	174	47	2	6.6	35.5	63	0.01
KL38-06	102	104.7	0.012		120	0.1	0.1	910	171	77	208	3	6	3.5	3.0	104	0.01
KL38-06	104.7	107.2	0.0229		229	0.08	0.1	610	134	52	40	5	4	4	1.6	43	0.01
KL38-06	107.2	110.8	0.0261		261	0.4	0.5	980	242	71	96	11	5	2.9	2.0	27	0.13
KL38-06	110.8	114.8	0.0029		29	0.32	0.1	2000	261	140	406	0.01	1	2.6	1.9	199	0.01
KL38-06	114.8	117.2	0.013		130	0.05	0.1	730	120	23	45	4	4	2.5	1.1	36	0.01
KL38-06	117.2	119.6	0.0092		92	0.19	0.1	2600	366	130	425	0.01	1	5.4	1.9	124	0.01
KL38-06	119.6	122.6	0.0046		46	0.23	0.6	3920	1020	210	363	1	1	7.8	2.3	187	0.01
KL38-06	122.6	125	0.06		600	0.2	0.1	3780	630	140	505	4	1	5.5	2.9	136	0.01
KL38-06	125	128.1	0.058		580	0.15	0.7	1700	275	130	247	0.01	1	4.7	1.7	39	0.01
KL38-06	128.1	130.5	0.146		1460	0.73	3.2	3630	510	630	510	9	10	44	9.0	100	0.2
KL38-06	130.5	134.7	0.0276		276	0.12	1.3	1580	254	51	120	11	1	5.3	4.0	43	0.17
KL38-06	134.7	137.6	0.0157		157	0.22	2	2920	900	55	115	11	4	4.5	3.2	41	0.24
KL38-06	137.6	140.3	0.0042		42	0.01	0.1	287	85	12	36	8	2	0.8	3.4	20	0.01
KL38-06	140.3	144.2	0.0041		41	0.01	0.1	271	72	13	27	7	3	2.3	1.9	16	0.01
KL38-06	144.2	147.2	0.0035		35	0.06	0.1	960	113	21	12	6	1	1.9	1.3	20	0.14
KL38-06	147.2	150	0.0125		125	0.05	0.1	520	62	29	18	6	6	1.3	1.5	20	0.01
KL38-06	150	153	0.015		150	0.03	0.1	500	91	43	25	4	8	3.7	2.1	19	0.01
KL38-06	153	156.3	0.0068		68	0.02	0.1	385	54	20	23	4	7	1.2	1.1	18	0.01
KL38-06	156.3	159	0.0067		67	0.04	0.1	590	71	21	18	5	4	1.3	0.8	19	0.01
KL38-06	159	161	0.067		670	0.09	0.1	1460	95	200	55	11	27	2.9	2.3	20	0.01
KL38-06	161	163.1	0.0301		301	0.08	0.1	3640	284	73	21	2	25	2.4	2.2	19	0.01
KL38-06	163.1	165.5	0.0261		261	0.39	0.1	11900	108	160	1160	2	68	4.4	4.4	26	0.2
KL38-06	165.5	168.7	0.015		150	0.35	0.1	460	47	44	720	4	5	3.2	1.5	25	0.01
KL38-06	168.7	172.8	0.042		420	0.24	2	1540	440	160	172	9	5	40	6.3	21	0.01
KL38-06	172.8	176.2	0.0107		107	0.08	0.6	850	128	18	52	7	2	7.4	2.1	13	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL38-06	176.2	180.2	0.0291	291	0.08	0.6	820	162	85	70	9	2	3.3	1.8	11	0.01
KL38-06	180.2	184.5	0.187	1870	0.16	3.2	1700	460	650	349	5	8	16.3	4.0	13	0.2
KL38-06	184.5	187.4	0.0229	229	0.06	0.6	1050	243	42	30	1	1	3.4	1.4	10	0.01
KL38-06	187.4	192.2	0.0112	112	0.08	0.1	710	640	31	44	1	1	2.4	1.3	13	0.01
KL38-06	192.2	195.3	0.0078	78	0.11	0.1	570	185	18	24	1	1	0.7	1.1	12	0.01
KL38-06	195.3	198	0.0225	225	0.06	0.1	1150	71	41	16	0.01	4	1.3	0.9	10	0.01
KL38-06	198	201	0.0382	382	0.06	0.7	1400	208	110	18	1	4	2.9	1.2	11	0.01
KL38-06	201	204	0.0148	148	0.05	0.1	720	123	21	19	0.01	3	1.1	0.8	9	0.01
KL38-06	204	207.5	0.0077	77	0.05	0.1	162	96	12	10	1	2	0.6	1.3	16	0.01
KL38-06	207.5	210.9	0.009	90	0.06	2.4	1500	1170	23	7	4	1	1.9	2.3	13	0.1
KL38-06	210.9	213.9	0.0316	316	0.05	1.2	520	348	24	8	1	3	2.3	1.0	12	0.1
KL38-06	213.9	219.1	0.242	2420	0.1	2.4	510	225	100	9	2	10	8.2	3.8	13	0.01
KL38-06	219.1	222.2	0.045	450	0.05	1.2	830	520	25	10	0.01	4	1.6	2.0	9	0.01
KL38-06	222.2	225.2	0.35	3500	0.15	13.9	11500	9600	36	28	5	13	12.8	7.5	14	0.01
KL38-06	225.2	228.2	0.524	5240	1.11	6.3	2900	740	350	131	4	26	20	6.0	13	0.01
KL38-06	228.2	231.2	1.05	10500	1.45	7.8	1600	540	160	35	2	42	7.2	9.5	14	0.01
KL38-06	231.2	234.2	0.536	5360	0.81	4	1000	142	73	8	2	27	3.2	5.0	12	0.01
KL38-06	234.2	237.2	0.0407	407	0.15	1	540	305	28	13	0.01	4	1.7	2.6	14	0.1
KL38-06	237.2	240	0.213	2130	0.18	1.2	1760	73	30	17	1	6	1.2	5.3	19	0.01
KL38-06	240	243	0.72	7200	0.67	3.9	2900	1030	200	10	2	28	7.1	8.5	17	0.1
KL38-06	243	246	0.0153	153	0.08	1.7	1160	1170	34	20	3	1	2	5.5	13	0.1
KL38-06	246	249	0.184	1840	0.23	2.5	2400	620	110	13	5	8	3.8	5.3	15	0.01
KL38-06	249	252.2	0.0218	218	0.09	1.8	1260	690	23	14	3	4	1.1	3.3	12	0.01
KL38-06	252.2	256.7	0.013	130	0.1	1.2	480	290	21	7	2	4	0.8	2.8	15	0.01
KL38-06	256.7	259.7	0.231	2310	0.18	1.7	400	128	68	9	5	5	2.8	5.1	20	0.1
KL38-06	259.7	263.8	0.89	8900	0.91	4.2	730	132	58	6	2	36	13.3	5.5	32	0.01
KL38-06	263.8	266.7	0.331	3310	0.58	2.1	770	115	41	20	1	13	6.3	3.8	21	0.01
KL38-06	266.7	268.7	0.0372	372	0.05	0.8	301	63	13	9	4	3	1	1.8	13	0.01
KL38-06	268.7	271.7	1.1	11000	0.48	2.4	500	168	50	14	3	27	8.4	3.7	27	0.01
KL38-06	271.7	275.7	0.124	1240	0.06	0.7	142	45	26	181	1	14	2.5	1.0	22	0.01
KL38-06	275.7	278.7	0.104	1040	0.11	1	76	55	47	2330	0.01	9	2.7	4.8	85	0.01
KL38-06	278.7	282.2	0.098	980	0.12	0.8	56	54	36	470	0.01	9	2.4	2.0	92	0.01
KL38-06	282.2	285.2	0.0372	372	0.14	0.6	61	47	42	1170	0.01	6	2.2	2.5	54	0.01
KL38-06	285.2	287.5	0.117	1170	0.07	0.9	58	28	15	36	1	6	1.9	1.5	21	0.01
KL38-06	287.5	290.6	0.092	920	0.07	1.4	72	44	30	107	4	6	2.5	1.3	32	0.01
KL38-06	290.6	292.3	0.73	7300	0.21	4.3	85	73	50	1150	3	15	3.4	4.5	36	0.01
KL38-06	292.3	294.9	1.68	16800	0.48	5.6	1070	97	6	54	30	38	3	7.0	18	0.01
KL38-06	294.9	296.7	0.73	7300	0.52	2.1	200	143	21	14	1	22	1.5	3.8	21	0.01
KL38-06	296.7	299.1	0.78	7800	0.39	3	650	358	34	42	1	32	1.6	3.3	22	0.01
KL38-06	299.1	302.2	0.6	6000	0.24	2.4	410	80	3	28	3	35	2	3.3	23	0.01
KL38-06	302.2	304.1	1.21	12100	0.57	5.8	329	68	33	8	1	41	4	8.3	21	0.01
KL38-06	304.1	306	0.148	1480	0.16	4.8	820	530	61	21	19	11	6.4	5.5	69	0.01
KL38-06	306	310.2	0.317	3170	0.4	4.4	235	146	70	27	14	32	5.2	5.5	26	0.01
KL38-06	310.2	315.2	0.344	3440	0.43	4	286	117	160	7	7	31	14.7	3.3	24	0.01
KL38-06	315.2	318.2	0.282	2820	0.29	4	85	95	150	3	10	34	4.2	5.5	22	0.01
KL38-06	318.2	321.2	0.533	5330	0.3	6.5	400	376	84	4	6	29	6.6	3.3	27	0.01
KL38-06	321.2	323.9	0.91	9100	0.72	3.4	271	120	55	12	3	66	5.3	12.5	21	0.01
KL38-06	323.9	326.5	0.203	2030	0.57	2.6	430	320	170	5	6	39	4	5.3	22	0.1
KL38-06	326.5	329.6	1.49	14900	0.96	16.4	177	142	32	23	7	82	2.8	22.2	34	0.01
KL38-06	329.6	332.7	0.82	8200	0.28	7.8	212	43	24	57	2	18	2.2	1.7	18	0.1
KL38-06	332.7	336.1	0.329	3290	0.63	6.1	2450	750	130	160	28	14	12.3	7.3	67	0.15
KL38-06	336.1	339	0.116	1160	0.79	7.3	3450	2860	170	192	40	7	37	7.5	58	0.46
KL38-06	339	341.5	1.52	15200	0.72	18.9	8500	6000	1980	25	5	64	13.2	8.5	38	0.1
KL38-06	341.5	343.5	0.282	2820	0.27	4.1	3760	2610	420	21	6	22	4.2	7.3	21	0.1
KL38-06	343.5	346.6	0.26	2600	0.47	6.5	5600	4800	320	28	26	1	4.5	15.9	23	0.01
KL38-06	346.6	348	2.88	28800	0.68	7.9	450	80	21	580	3	40	3.5	6.0	26	0.01
KL38-06	348	351	2.21	22100	0.44	4.6	358	98	10	2400	6	38	3.3	1.5	18	0.1
KL38-06	351	354	1.88	18800	1.02	4.7	700	390	6	770	19	35	2.1	1.0	24	0.01
KL38-06	354	357	2.73	27300	1.72	6.9	4000	4000	9	14	8	40	3.8	10.0	32	0.01
KL38-06	357	360	2.01	20100	2.39	4.3	950	2100	4	22	8	28	3.9	8.5	23	0.1
KL38-06	360	363	2.85	28500	3.18	7.3	1000	720	5	51	12	34	2.8	8.0	21	0.01
KL38-06	363	366	3.4	34000	4.18	9.6	1490	440	42	6	5	49	24.2	20.0	89	0.1
KL38-06	366	368.8	3.15	31500	1.36	14.6	3400	2100	470	13	5	45	46	24.5	106	0.1

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL38-06	368.8	372.2	1.2	12000	0.27	5.6	227	124	21	42	2	14	0.8	15.0	60	0.01
KL38-06	372.2	375.2	0.79	7900	0.2	3	113	75	27	64	3	12	1.4	14.0	83	0.38
KL38-06	375.2	378.2	1.02	10200	0.15	2.6	188	67	9	79	2	7	0.9	15.5	76	0.15
KL38-06	378.2	381	0.61	6100	0.13	2.6	85	49	14	115	4	13	0.7	17.3	54	0.11
KL38-06	381	385.85	0.72	7200	0.18	2.3	67	41	13	25	7	10	0.8	16.0	77	0.1
KL38-06	385.85	387	0.67	6700	0.22	2.2	66	35	40	13	10	14	5	13.8	50	0.13
KL38-06	387	390	0.89	8900	0.21	2.7	70	45	15	76	7	11	0.9	14.0	74	0.1
KL38-06	390	393	1.11	11100	0.17	2.9	80	56	18	24	5	11	0.8	25.5	86	0.17
KL38-06	393	396	0.59	5900	0.16	6.9	123	54	13	132	37	9	0.7	9.8	75	0.01
KL38-06	396	399	0.496	4960	0.13	3.9	58	47	12	24	40	8	0.6	11.0	97	0.01
KL38-06	399	402	0.456	4560	0.21	2	46	54	11	18	10	11	0.6	8.5	96	0.01
KL38-06	402	405	1.12	11200	0.2	6.9	387	113	1440	16	6	12	5.6	24.0	54	0.11
KL38-06	405	408	0.514	5140	0.3	16.8	200	61	790	200	5	12	6.7	7.5	121	0.1
KL38-06	408	411.2	0.193	1930	0.08	1.5	63	16	90	16	3	8	0.6	2.5	70	0.01
KL38-06	411.2	414.2	0.2	2000	0.16	1.2	55	16	7	26	1	7	0.4	2.0	63	0.01
KL38-06	414.2	417.2	0.247	2470	0.13	1.3	55	18	1	39	4	6	0.4	2.8	57	0.01
KL38-06	417.2	420.2	0.173	1730	0.08	1	54	23	5	75	1	6	0.5	2.3	50	0.01
KL38-06	420.2	423	0.24	2400	0.11	1.7	46	23	4	34	6	6	0.3	2.8	72	0.01
KL38-06	423	426.2	0.32	3200	0.13	2.1	60	20	6	29	4	8	0.6	4.2	76	0.01
KL38-06	426.2	429	0.7	7000	0.4	3.5	113	40	15	38	5	10	5	9.0	112	0.01
KL38-06	429	432	0.46	4600	0.17	2.2	40	18	11	224	9	9	0.5	8.6	102	0.01
KL38-06	432	435.4	0.202	2020	0.12	1.3	59	16	4	39	1	7	0.2	2.6	60	0.01
KL38-06	435.4	441	0.3	3000	0.18	2.4	115	55	28	43	2	11	0.7	6.6	78	0.01
KL38-06	441	444	0.29	2900	0.2	1	50	14	11	10	1	9	0.3	3.3	62	0.01
KL38-06	444	447.1	1.01	10100	0.38	4.6	44	26	6	14	2	11	0.8	6.6	72	0.01
KL38-06	447.1	450.5	1.54	15400	0.66	2.6	144	14	2	18	0.01	16	0.3	10.5	72	0.01
KL38-06	450.5	453.2	0.42	4200	0.09	1	108	39	6	47	0.01	1	0.4	4.4	258	0.01
KL38-06	453.2	456.2	0.32	3200	0.05	0.6	202	60	42	340	0.01	1	0.5	3.0	332	0.01
KL38-06	456.2	459.2	0.21	2100	0.05	0.1	92	32	40	850	0.01	1	0.6	3.7	240	0.01
KL38-06	459.2	462.2	0.25	2500	0.04	0.9	480	90	190	920	0.01	1	3.4	3.4	329	0.28
KL38-06	462.2	465.2	0.52	5200	0.09	0.7	51	22	8	115	0.01	5	0.5	4.6	150	0.15
KL38-06	465.2	468.2	0.33	3300	0.03	0.1	58	11	3	65	0.01	1	0.2	2.2	245	0.01
KL38-06	468.2	471	0.28	2800	0.01	0.1	152	26	8	160	0.01	1	0.3	2.1	231	0.01
KL38-06	471	474	0.332	3320	0.03	0.1	66	16	8	60	0.01	3	0.01	2.2	230	0.01
KL38-06	474	476.5	0.43	4300	0.02	0.1	44	12	3	241	0.01	4	0.01	2.9	281	0.01
KL38-06	476.5	478.9	0.66	6600	0.01	0.9	36	17	5	920	0.01	4	0.2	3.2	194	0.01
KL38-06	478.9	481.8	0.65	6500	0.06	1.1	148	52	140	168	0.01	1	1	3.2	216	0.16
KL38-06	481.8	486.2	0.59	5900	0.04	0.6	27	10	12	238	0.01	1	0.6	3.0	251	0.01
KL38-06	486.2	489.2	0.48	4800	0.03	0.6	201	41	22	72	0.01	2	0.2	2.4	203	0.01
KL38-06	489.2	492	0.402	4020	0.03	0.7	145	52	8	53	0.01	1	0.2	3.4	253	0.01
KL38-06	492	495	0.27	2700	0.07	0.5	225	86	13	34	0.01	4	0.5	3.0	187	0.01
KL38-06	495	497.3	0.28	2800	0.01	0.1	75	18	3	81	0.01	3	0.2	2.4	198	0.01
KL38-07	0	3.2	0.0047	47	0.14	0.1	148	34	13	3	0.01	1	0.3	0.8	19	0.01
KL38-07	3.2	6.2	0.004	40	0.12	0.9	180	34	29	4	0.01	1	0.2	0.7	16	0.01
KL38-07	6.2	12.2	0.0031	31	0.16	0.1	240	88	65	2	0.01	1	0.3	0.5	18	0.01
KL38-07	12.2	15.2	0.0038	38	0.23	0.1	670	178	26	3	0.01	1	1.2	2.1	22	0.01
KL38-07	15.2	18.2	0.0036	36	0.19	0.1	920	211	73	3	0.01	1	1.1	1.8	21	0.01
KL38-07	18.2	21.2	0.0027	27	0.07	0.1	303	106	15	5	0.01	1	0.5	2.4	15	0.01
KL38-07	21.2	24.2	0.0021	21	0.24	0.1	268	185	10	4	0.01	1	1.2	3.3	40	0.01
KL38-07	24.2	27.2	0.0082	82	0.04	0.1	184	75	7	4	0.01	1	0.01	1.0	32	0.01
KL38-07	27.2	30.2	0.001	10	0.01	0.1	73	30	3	3	0.01	1	0.01	0.0	23	0.01
KL38-07	30.2	33.2	0.006	60	0.01	0.1	160	103	10	3	0.01	1	0.2	0.8	25	0.01
KL38-07	33.2	36.2	0.0026	26	0.01	0.1	171	85	5	2	0.01	1	0.2	0.8	37	0.01
KL38-07	36.2	39.2	0.0048	48	0.06	0.1	420	302	44	6	0.01	1	2.9	1.0	26	0.01
KL38-07	39.2	42.2	0.0082	82	0.01	0.1	289	110	9	3	0.01	1	1.2	0.6	61	0.01
KL38-07	42.2	45.2	0.0105	105	0.03	0.1	460	151	9	6	0.01	1	0.8	1.3	45	0.01
KL38-07	45.2	48.2	0.0231	231	0.03	0.1	155	87	5	3	0.01	1	0.2	0.8	27	0.01
KL38-07	48.2	51.2	0.0076	76	0.01	0.1	83	24	7	5	0.01	1	0.2	0.8	43	0.01
KL38-07	51.2	54.2	0.0049	49	0.01	0.1	49	48	6	5	0.01	1	0.01	1.0	29	0.01
KL38-07	54.2	57.2	0.0096	96	0.02	0.1	101	39	7	4	0.01	1	0.01	2.0	17	0.01
KL38-07	57.2	60.2	0.0054	54	0.01	0.1	62	44	4	3	0.01	1	0.01	0.8	16	0.01
KL38-07	60.2	63.2	0.0028	28	0.07	1.1	920	1680	6	6	0.01	1	1.9	16.5	22	0.01
KL38-07	63.2	66.2	0.0027	27	0.01	0.1	78	36	5	9	0.01	1	0.3	1.2	27	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL38-07	66.2	69.1	0.005		50	0.04	0.1	530	490	6	16	0.01	1	1.5	2.0	18	0.01
KL38-07	69.1	72.2	0.0102		102	0.03	1.3	2420	1460	8	10	0.01	1	3.7	3.8	18	0.01
KL38-07	72.2	75.2	0.0167		167	0.33	3.4	7800	4100	29	5	0.01	1	7.7	15.3	18	0.17
KL38-07	75.2	78.2	0.0032		32	0.05	0.1	760	620	7	2	0.01	1	1.7	2.3	20	0.01
KL38-07	78.2	81.2	0.0057		57	0.06	0.1	420	344	18	5	0.01	1	2	2.4	23	0.01
KL38-07	81.2	84.2	0.0021		21	0.07	0.1	620	490	6	1	0.01	1	1	1.5	23	0.1
KL38-07	84.2	87.2	0.0022		22	0.05	0.7	810	1050	7	5	0.01	1	1.9	6.3	22	0.1
KL38-07	87.2	90.2	0.0032		32	0.17	0.7	860	500	18	6	0.01	1	3.7	3.6	26	0.15
KL38-07	90.2	93.2	0.0026		26	0.06	0.1	104	72	9	3	0.01	1	1.1	1.2	23	0.01
KL38-07	93.2	96.2	0.004		40	0.08	0.1	187	110	14	5	0.01	1	1.8	2.5	21	0.01
KL38-07	96.2	100.8	0.0073		73	0.79	4.4	2430	2690	85	10	0.01	3	14.8	19.4	37	0.28
KL38-07	100.8	104.6	0.0098		98	0.34	1.4	740	610	41	18	1	4	3.8	10.8	46	0.16
KL38-07	104.6	107	0.0069		69	0.75	8.4	900	510	240	67	140	10	13.6	19.9	70	0.15
KL38-07	107	109.9	0.0047		47	0.2	0.6	1280	275	32	10	3	1	2.2	9.0	41	0.01
KL38-07	109.9	116	0.0047		47	0.13	1.5	1740	1470	28	5	2	3	3.1	7.5	28	0.27
KL38-07	116	120.2	0.0121		121	0.12	1.4	460	378	61	12	4	3	3.6	5.8	74	0.01
KL38-07	120.2	123.2	0.0231		231	0.16	0.9	690	830	120	8	2	3	5.7	5.3	93	0.01
KL38-07	123.2	126	0.0129		129	0.11	0.1	352	178	50	5	1	1	2.2	2.1	69	0.01
KL38-07	126	128.4	0.0243		243	0.09	0.1	530	175	62	12	0.01	4	5.3	2.1	85	0.01
KL38-07	128.4	131.2	1.43		14300	0.28	7.2	269	130	3200	440	5	13	370	13.5	301	0.28
KL38-07	131.2	135.2	1.87		18700	0.52	12.6	1330	410	2120	185	8	1	170	16.5	240	0.32
KL38-07	135.2	139.3	0.0387		387	0.25	1.3	3030	930	140	90	5	2	19.6	3.9	153	0.15
KL38-07	139.3	143.3	0.051		510	0.07	1.2	1100	324	170	28	2	1	12.6	2.0	93	0.01
KL38-07	143.3	147	0.0147		147	0.09	0.8	2760	800	40	30	1	1	7.8	2.2	55	0.1
KL38-07	147	150.2	0.0171		171	0.28	0.9	6300	1570	52	51	1	3	9.5	5.0	89	0.12
KL38-07	150.2	153.2	0.092		920	0.19	1	3960	1260	300	440	4	4	14.7	7.5	204	0.11
KL38-07	153.2	156.2	0.0275		275	0.12	0.6	1320	450	98	156	1	1	12.1	4.3	201	0.01
KL38-07	156.2	159.2	0.0133		133	0.17	0.9	3090	1030	87	171	1	3	4.5	7.5	214	0.01
KL38-07	159.2	162.2	0.0106		106	0.2	1	5170	1490	180	178	1	4	9.6	9.0	166	0.13
KL38-07	162.2	165.2	0.0196		196	0.19	1.1	4190	1380	81	650	1	5	8.1	14.3	163	0.19
KL38-07	165.2	168.2	0.044		440	0.23	1.3	5330	1670	240	770	1	6	9.3	13.0	182	0.01
KL38-07	168.2	171.2	0.043		430	0.15	0.9	2480	770	37	273	0.01	2	2.9	6.5	49	0.01
KL38-07	171.2	174.2	0.0313		313	0.17	0.5	2320	380	85	630	1	3	8.6	7.3	89	0.01
KL38-07	174.2	177.2	0.203		2030	0.21	0.9	3690	740	470	318	2	8	14.8	9.3	118	0.12
KL38-07	177.2	180.2	0.192		1920	0.23	2.4	7100	710	590	223	4	12	120	9.6	113	0.19
KL38-07	180.2	183.2	0.042		420	0.09	0.7	1710	369	150	550	1	5	11.5	5.3	79	0.18
KL38-07	183.2	186.2	1		10000	0.25	4.2	7200	1410	890	900	4	63	50	11.8	262	0.15
KL38-07	186.2	189.2	0.29		2900	0.19	4	15100	2200	900	86	6	15	120	11.8	54	0.25
KL38-07	189.2	192.2	0.7		7000	0.36	10.8	23600	5200	2050	219	8	45	80	16.8	91	0.42
KL38-07	192.2	194.6	0.052		520	0.08	2	3020	411	110	143	3	3	36	6.5	27	0.01
KL38-07	194.6	197.5	0.25		2500	0.17	2.4	15100	354	68	57	4	33	12.7	11.6	30	0.13
KL38-07	197.5	199.5	0.084		840	0.29	13.2	6400	6900	170	249	16	9	100	11.5	17	0.34
KL38-07	199.5	202.4	0.0102		102	0.13	2.3	4460	690	33	78	9	10	6.7	10.4	26	0.01
KL38-07	202.4	205.7	0.006		60	0.11	1.2	2710	375	14	41	7	6	3.7	11.0	22	0.01
KL38-07	205.7	208.7	0.0174		174	0.13	1.5	2310	430	35	25	18	7	3.4	7.0	24	0.01
KL38-07	208.7	210.9	0.0106		106	0.09	5.9	6800	3600	38	5	26	4	19.8	8.0	23	0.19
KL38-07	210.9	213.2	0.083		830	0.37	22	37600	6100	230	28	44	65	100	19.0	22	0.9
KL38-07	213.2	216.2	0.0045		45	0.05	1.9	2150	460	8	21	24	1	2.5	5.4	22	0.01
KL38-07	216.2	219.2	0.0121		121	0.06	1.8	1900	560	16	30	5	1	13.6	3.8	23	0.01
KL38-07	219.2	222.2	0.0157		157	0.1	4	5080	1410	30	37	4	9	11.3	6.8	18	0.12
KL38-07	222.2	225.2	0.0046		46	0.11	5.9	5230	2240	30	29	1	3	17.1	4.8	14	0.23
KL38-07	225.2	228.2	0.0042		42	0.03	2.1	2640	1850	14	8	1	1	3	5.5	10	0.01
KL38-07	228.2	231.2	0.0037		37	0.02	2	620	450	7	13	2	1	1	4.0	11	0.01
KL38-07	231.2	234.1	0.0033		33	0.01	0.6	172	114	2	13	1	1	0.2	0.9	10	0.01
KL38-07	234.1	237.7	0.0024		24	0.01	0.9	550	312	3	9	2	1	1.1	5.3	10	0.01
KL38-07	237.7	240.1	0.0074		74	0.01	0.5	123	156	1	6	0.01	1	0.01	1.8	12	0.01
KL38-07	240.1	243.2	0.0029		29	0.01	0.7	128	256	3	7	1	1	0.2	1.9	10	0.01
KL38-07	243.2	246.2	0.0015		15	0.01	0.1	72	50	0.01	3	0.01	1	0.01	0.7	8	0.01
KL38-07	246.2	250.1	0.0191		191	0.01	1.5	440	2510	10	7	1	1	4.8	2.0	12	0.01
KL38-07	250.1	253.3	0.0114		114	0.21	2.8	5390	1340	53	12	4	2	9.8	6.8	14	0.24
KL38-07	253.3	256.3	0.005		50	0.05	1.2	1540	520	8	2	2	1	1.8	3.8	12	0.01
KL38-07	256.3	259.2	0.096		960	0.02	1	1060	279	41	6	5	4	6.2	3.1	12	0.01
KL38-07	259.2	262.2	0.0113		113	0.03	3.1	3290	5000	14	4	1	3	3.4	6.2	12	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL38-07	262.2	266.7	0.0054		54	0.07	3.1	490	1310	12	13	5	1	3.7	6.0	15	0.01
KL38-07	266.7	269.3	0.0053		53	0.03	1.5	309	251	21	15	12	1	1.3	3.0	14	0.01
KL38-07	269.3	271.9	0.0042		42	0.01	0.1	133	143	13	2	1	1	0.2	2.1	20	0.01
KL38-07	271.9	274.9	0.0043		43	0.01	1.1	251	220	6	6	2	1	0.7	2.6	18	0.01
KL38-07	274.9	277.2	0.0039		39	0.04	4.5	152	297	14	14	31	1	2.9	4.0	17	0.01
KL38-07	277.2	280.1	0.0206		206	0.04	3.1	460	810	47	20	5	1	12.8	7.3	20	0.01
KL38-07	280.1	283	0.0221		221	0.07	1.4	1210	312	110	8	2	1	3	5.3	15	0.01
KL38-07	283	286	0.77		7700	0.24	23.4	14400	18000	640	35	4	8	75	40.5	19	1
KL38-07	286	289.5	0.48		4800	0.36	410	43000	250000	1370	52	450	5	375	850.0	34	0.96
KL38-07	289.5	292.4	0.056		560	0.51	6.6	2840	1530	95	8	6	3	10.8	9.6	12	0.27
KL38-07	292.4	294.6	0.135		1350	0.04	1.1	800	350	76	14	20	2	8.3	6.1	16	0.1
KL38-07	294.6	296.8	0.0134		134	0.01	0.8	450	285	6	10	1	1	0.7	2.7	13	0.01
KL38-07	296.8	299.9	0.0114		114	0.01	1.5	345	357	17	6	1	1	3.6	3.2	14	0.01
KL38-07	299.9	303	0.05		500	0.01	1.7	1810	370	16	7	6	1	1.8	4.8	20	0.1
KL38-07	303	306	0.0094		94	0.01	0.1	349	301	6	10	1	1	0.6	3.3	15	0.01
KL38-07	306	309.3	0.08		800	0.15	3	470	110	14	12	0.01	2	1.6	13.0	20	0.01
KL38-07	309.3	312	0.35		3500	0.41	3.9	490	44	41	8	1	21	3.5	15.2	30	0.01
KL38-08	113.5	116.5	0.062		620	0.15	3.2	890	470	120	7	17	4	7.3	6.0	51	0.11
KL38-08	116.5	119.1	0.042		420	0.08	0.9	530	500	69	8	6	1	5.9	2.5	79	0.01
KL38-08	119.1	121.7	0.0131		131	0.12	0.8	500	570	71	10	2	2	4.7	3.3	94	0.1
KL38-08	121.7	124.1	0.0311		311	0.1	0.7	710	440	89	60	2	4	6.3	5.1	103	0.01
KL38-08	124.1	126	0.0247		247	0.15	0.8	890	328	74	72	2	5	6.1	4.0	83	0.01
KL38-08	126	128.9	1.95		19500	0.32	7.6	520	161	3700	360	10	17	450	15.0	213	0.51
KL38-08	128.9	133.1	1.17		11700	0.33	9.4	890	388	1880	291	16	2	212	15.3	192	0.39
KL38-08	133.1	136.1	0.058		580	0.29	2.1	4000	1140	130	128	5	1	42	5.0	105	0.18
KL38-08	136.1	139.6	0.64		6400	0.25	5.8	1470	490	1200	151	9	1	130	10.5	161	0.26
KL38-08	139.6	142.6	0.14		1400	0.13	1.5	4100	1030	420	194	2	2	59	4.8	176	0.13
KL38-08	142.6	145.1	0.0251		251	0.11	0.8	3400	980	73	35	2	2	18	5.2	178	0.14
KL38-08	145.1	148.1	0.0135		135	0.14	0.7	4000	1150	58	58	2	1	8.9	4.3	184	0.1
KL38-08	148.1	151.1	0.19		1900	0.17	1.1	5500	1300	730	342	2	5	34	7.4	171	0.12
KL38-08	151.1	154.1	0.025		250	0.09	0.1	1610	480	64	168	1	2	10.1	2.8	89	0.01
KL38-08	154.1	157.1	0.0155		155	0.12	0.7	2900	710	68	167	1	2	7.9	5.0	216	0.1
KL38-08	157.1	160.1	0.0273		273	0.3	1.4	7700	1660	150	259	2	3	26	8.5	162	0.19
KL38-08	160.1	164.6	0.0176		176	0.26	1.5	5300	1540	150	570	2	3	14	8.8	154	0.1
KL38-08	164.6	167.1	0.23		2300	0.32	2.3	6800	1760	720	730	6	8	24	12.8	86	0.14
KL38-08	167.1	169.1	0.0262		262	0.09	0.7	800	192	36	560	1	2	2.8	3.0	39	0.01
KL38-08	169.1	172.1	0.0273		273	0.08	0.8	890	299	64	920	3	3	4.2	5.0	48	0.01
KL38-08	172.1	175.3	0.23		2300	0.17	1	3500	930	610	620	2	7	19.5	8.0	113	0.12
KL38-08	175.3	178.1	0.112		1120	0.1	1.3	3100	550	370	39	3	10	48	5.5	109	0.1
KL38-08	178.1	181.6	0.0389		389	0.13	1	940	220	110	980	2	7	13.4	7.3	64	0.01
KL38-08	181.6	183.7	0.0239		239	0.11	1.3	1730	344	74	1700	2	12	10.5	6.8	118	0.01
KL38-08	183.7	186.7	0.128		1280	0.16	2.5	10000	2040	460	59	4	13	30	8.5	60	0.2
KL38-08	186.7	190.1	0.44		4400	0.16	5.9	18000	870	1100	128	4	45	90	11.0	51	0.43
KL38-08	190.1	193.1	0.32		3200	0.07	3	5000	680	660	190	6	16	45	6.0	29	0.12
KL38-08	193.1	196.4	0.23		2300	0.37	2.9	12700	291	100	91	8	30	6.1	14.0	31	0.1
KL38-08	196.4	199.7	0.0146		146	0.08	1.3	1050	182	30	95	6	6	6.5	4.3	24	0.01
KL38-08	199.7	202.7	0.0048		48	0.07	0.7	650	116	12	37	9	4	1.7	4.5	26	0.01
KL38-08	202.7	205.1	0.098		980	0.39	5.2	18600	1030	190	41	20	87	42	18.5	29	0.23
KL38-08	205.1	208.1	0.063		630	0.22	2.2	7400	430	71	120	14	33	15.5	17.1	37	0.11
KL38-08	208.1	210.8	0.0216		216	0.09	1.6	4300	640	30	30	10	8	14.9	5.3	27	0.1
KL38-08	210.8	214.1	0.065		650	0.16	4.7	17200	1420	120	14	12	74	43	10.0	31	0.24
KL38-08	214.1	216.8	0.041		410	0.36	9.7	13500	3800	130	74	4	3	60	6.3	26	0.3
KL38-08	216.8	219.8	0.0203		203	0.14	3.6	6600	1400	41	61	4	17	12.9	6.3	26	0.13
KL38-08	219.8	222.8	0.0235		235	0.07	1.6	3400	450	32	32	7	12	37	3.5	23	0.11
KL38-08	222.8	225.7	0.0042		42	0.04	1.7	1670	1340	10	10	2	1	1.3	4.0	16	0.01
KL38-08	225.7	228.8	0.0018		18	0.03	0.8	1900	750	23	10	1	1	5	2.8	13	0.01
KL38-08	228.8	231.4	0.002		20	0.03	1.4	980	323	16	14	2	1	2.1	2.8	12	0.01
KL38-08	231.4	234.3	0.0021		21	0.02	1.2	1880	620	9	13	1	1	2.7	2.5	11	0.01
KL38-08	234.3	237.8	0.0078		78	0.06	1.7	610	320	13	17	7	1	4.3	6.6	15	0.01
KL38-08	237.8	241.1	0.0051		51	0.02	0.7	242	132	6	9	1	1	1.6	2.3	14	0.01
KL38-08	241.1	244.1	0.0047		47	0.01	0.8	530	510	12	10	1	1	1	5.5	11	0.01
KL38-08	244.1	247.1	0.0171		171	0.09	1.2	1620	510	30	7	4	1	6.3	4.5	15	0.01
KL38-08	247.1	250.1	0.0042		42	0.04	0.6	910	480	13	8	1	2	1.4	3.3	15	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL38-08	250.1	253.1	0.0071		71	0.03	0.8	237	226	16	9	1	1	3.8	1.3	13	0.01
KL38-08	253.1	256.1	0.0076		76	0.03	0.8	490	211	15	6	2	1	5.5	2.8	14	0.01
KL38-08	256.1	259.2	0.047		470	0.07	1.2	1100	336	59	16	2	5	9.3	4.3	13	0.01
KL38-08	259.2	262.6	0.0055		55	0.05	1.4	660	1050	12	3	3	3	4.9	4.8	14	0.01
KL38-08	262.6	265.1	0.0037		37	0.04	1.2	520	660	15	7	3	1	2.9	3.8	14	0.01
KL38-08	265.1	268.1	0.0091		91	0.04	1.5	660	318	24	15	10	3	2.7	5.8	15	0.1
KL38-08	268.1	270.9	0.0076		76	0.04	2.1	610	346	16	12	19	1	3.7	5.5	17	0.01
KL38-08	270.9	274	0.0285		285	0.05	1.7	540	272	60	9	8	1	36	4.8	17	0.01
KL38-08	274	277.1	0.0139		139	0.15	1.8	1120	670	45	15	6	2	24	9.1	19	0.01
KL38-08	277.1	280.1	0.26		2600	0.12	4.7	3300	1100	700	46	4	5	90	9.0	18	0.16
KL38-08	280.1	283.3	0.67		6700	0.21	131	74000	101000	510	32	5	9	148	130.0	71	0.75
KL38-08	283.3	286.1	0.72		7200	0.35	19	25400	27000	680	26	7	12	96	36.0	18	1.52
KL38-08	286.1	288.9	0.13		1300	0.67	17	15600	8100	160	17	23	4	66	49.0	36	0.96
KL38-08	288.9	292.1	0.069		690	0.08	1.1	810	224	32	5	2	4	1.4	4.2	20	0.01
KL38-08	292.1	295.1	0.046		460	0.05	0.8	730	184	43	9	3	2	7.8	3.3	16	0.1
KL38-08	295.1	298.1	0.084		840	0.05	1.6	4200	890	71	9	2	2	16	6.3	20	0.24
KL38-08	298.1	301.1	0.062		620	0.03	0.8	580	246	36	5	0.01	2	3.5	3.5	20	0.01
KL38-08	301.1	304.9	0.182		1820	0.09	1.4	830	194	56	13	0.01	7	5.7	4.5	19	0.11
KL38-08	304.9	307.1	0.116		1160	0.35	3.5	11200	2900	170	10	1	5	13.8	15.3	26	0.36
KL38-08	307.1	310.1	0.37		3700	0.42	2.8	420	71	70	11	0.01	7	4.1	7.5	26	0.01
KL38-08	310.1	313.1	0.31		3100	0.29	1.1	480	60	29	12	1	9	1.2	9.2	28	0.01
KL38-08	313.1	315.4	0.33		3300	0.23	2.1	1250	560	32	32	0.01	14	3.9	9.2	21	0.01
KL38-08	315.4	319.1	0.21		2100	0.17	2.6	840	560	58	276	4	11	5	11.0	75	0.01
KL38-08	319.1	321.7	0.34		3400	0.63	6	730	329	130	152	107	12	7	16.0	101	0.01
KL38-08	321.7	324	0.27		2700	0.16	1.3	105	27	16	450	1	8	1.7	5.2	90	0.01
KL38-08	324	326.6	0.24		2400	0.15	1.6	156	76	22	190	0.01	8	1.8	8.2	59	0.15
KL38-08	326.6	328.1	0.173		1730	0.07	0.6	107	45	23	158	0.01	3	1.4	2.5	20	0.01
KL38-08	328.1	331	0.28		2800	0.14	0.6	417	48	22	148	0.01	14	0.5	4.8	31	0.01
KL38-08	331	334.1	0.51		5100	0.26	1.2	700	41	21	28	1	26	1.7	5.0	28	0.01
KL38-08	334.1	337.1	0.88		8800	0.32	3.1	720	62	18	26	30	43	6.2	6.8	18	0.01
KL38-08	337.1	339.9	0.151		1510	0.05	0.7	345	29	11	38	1	20	1.3	4.2	19	0.01
KL38-08	339.9	343.1	0.63		6300	0.22	2.2	297	42	17	18	0.01	38	1.7	6.1	37	0.01
KL38-08	343.1	346.1	0.97		9700	0.36	2.5	354	81	15	32	0.01	17	1.8	4.0	19	0.01
KL38-08	346.1	350.7	0.45		4500	0.54	1.7	1160	203	26	23	0.01	22	4.1	6.5	28	0.01
KL38-08	350.7	355.1	0.4		4000	0.17	1	7900	68	15	21	1	30	1.7	6.5	26	0.01
KL38-08	355.1	358.1	0.54		5400	0.38	1.2	4650	83	37	13	0.01	37	3.7	6.2	26	0.01
KL38-08	358.1	361	0.18		1800	0.18	0.7	229	51	46	46	0.01	4	6.9	1.9	16	0.01
KL38-08	361	364.1	0.22		2200	0.18	0.6	1900	40	22	254	1	9	3.8	3.0	23	0.01
KL38-08	364.1	367.1	0.31		3100	0.28	1.3	147	67	31	152	5	4	4.5	3.2	23	0.01
KL38-08	367.1	370.1	0.48		4800	0.32	1.8	460	27	36	19	1	8	1.1	4.0	20	0.01
KL38-08	370.1	374.7	2.48		24800	0.27	5.7	373	24	19	12	2	52	4.5	3.0	21	0.01
KL38-08	374.7	377.7	0.195		1950	0.12	1	194	30	22	11	0.01	1	0.6	2.3	15	0.01
KL38-08	377.7	381.2	0.144		1440	0.09	0.8	169	33	24	14	0.01	1	0.7	0.7	16	0.01
KL38-08	381.2	384.5	0.073		730	0.07	0.5	195	40	31	8	0.01	1	0.8	0.6	19	0.01
KL38-08	384.5	387.5	0.074		740	0.07	0.6	1070	34	19	3	0.01	1	1	0.6	17	0.01
KL38-08	387.5	391	0.141		1410	0.14	0.9	420	62	18	2	0.01	1	1.2	1.2	14	0.01
KL38-08	391	394.1	1.09		10900	0.45	3.5	239	34	6	3	12	20	4.3	3.5	19	0.01
KL38-08	394.1	397.1	0.81		8100	0.25	1.5	318	9	1	12	3	30	2.5	1.8	22	0.01
KL38-08	397.1	400.1	1.46		14600	0.73	2.4	10200	11	3	16	5	159	4.5	5.0	28	0.01
KL38-08	400.1	403.1	2.25		22500	0.97	3.7	192	12	14	73	5	24	0.6	18.0	52	0.01
KL38-08	403.1	406.1	2.12		21200	1.25	5.7	379	11	0.01	9	9	53	1.2	5.5	33	0.01
KL38-08	406.1	409.1	3.51		35100	2.04	7.2	294	20	0.01	3	10	56	1	8.5	17	0.01
KL38-08	409.1	412.1	3.72		37200	2.72	7.3	460	65	58	7	4	66	4.8	8.5	41	0.1
KL38-08	412.1	415.4	2.94		29400	3.43	12.5	386	88	28	8	7	51	5.2	9.0	40	0.01
KL38-08	415.4	417.5	1.31		13100	1.51	26.4	750	2600	56	10	12	28	6.1	9.5	95	0.1
KL38-08	417.5	418.9	0.92		9200	0.87	14.4	860	1360	23	68	5	9	2.5	7.2	58	0.1
KL38-08	418.9	421.2	0.5		5000	0.3	3.1	590	203	5	6	2	6	0.01	4.5	62	0.01
KL38-08	421.2	423.9	0.87		8700	0.26	5.8	276	268	10	13	4	11	0.7	9.1	116	0.01
KL38-08	423.9	427.1	0.48		4800	0.53	1.9	142	41	1	9	1	9	0.6	4.3	104	0.01
KL38-08	427.1	430.1	0.45		4500	0.25	1.1	81	28	2	63	0.01	7	0.01	2.2	75	0.01
KL38-08	430.1	433.9	0.45		4500	0.22	1.2	232	86	3	69	0.01	7	0.2	2.8	89	0.01
KL38-08	433.9	437.2	0.32		3200	0.17	0.8	93	25	2	12	0.01	7	0.01	4.1	82	0.01
KL38-08	437.2	439.2	0.26		2600	0.21	0.8	47	17	3	40	0.01	4	0.01	1.5	68	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL38-08	439.2	442.1	0.22	2200	0.15	0.6	71	18	2	19	0.01	5	0.01	1.8	68	0.01
KL38-08	442.1	445.1	0.36	3600	0.11	1.4	107	42	2	11	1	6	0.01	2.8	89	0.01
KL38-08	445.1	448.1	0.62	6200	0.19	11.4	245	366	21	19	20	5	1.2	3.2	87	0.01
KL38-08	448.1	451.1	0.27	2700	0.18	1.4	91	29	1	51	1	5	0.01	2.0	52	0.01
KL38-08	451.1	454.1	0.28	2800	0.09	1.3	58	21	1	8	1	5	0.01	2.5	73	0.01
KL38-08	454.1	457.1	0.42	4200	0.25	1	117	81	1	38	2	5	0.01	4.7	61	0.01
KL38-08	457.1	460.1	0.36	3600	0.32	0.9	58	20	1	15	0.01	4	0.01	2.5	65	0.01
KL38-08	460.1	463.1	0.28	2800	0.22	0.9	56	18	3	14	0.01	4	0.01	1.5	67	0.01
KL38-08	463.1	466.1	0.24	2400	0.21	0.7	44	15	2	10	1	3	0.01	1.6	53	0.01
KL38-08	466.1	469.1	0.42	4200	0.21	1.4	54	15	2	60	2	4	0.01	2.3	49	0.01
KL38-08	469.1	472.1	0.3	3000	0.25	1.3	50	16	11	22	1	6	0.01	2.5	49	0.01
KL38-08	472.1	475.1	0.36	3600	0.24	0.9	61	21	2	113	0.01	4	0.01	3.0	63	0.01
KL38-08	475.1	478.1	0.198	1980	0.1	0.1	43	14	1	28	0.01	3	0.01	1.5	67	0.01
KL38-08	478.1	481.1	0.27	2700	0.13	1.8	361	264	2	9	2	5	0.01	2.4	58	0.01
KL38-08	481.1	484.2	0.147	1470	0.07	1.7	520	268	2	6	3	3	0.01	1.2	72	0.01
KL38-08	484.2	487.1	0.23	2300	0.12	0.6	36	16	1	11	0.01	4	0.01	2.0	73	0.01
KL38-08	487.1	490.1	0.62	6200	0.32	1.4	77	18	8	15	1	10	0.01	4.8	87	0.01
KL38-08	490.1	493.1	0.36	3600	0.43	1.8	106	43	7	8	3	8	0.01	3.0	69	0.01
KL38-08	493.1	496.1	0.26	2600	0.54	0.7	281	40	6	5	0.01	12	0.01	2.0	55	0.01
KL38-08	496.1	499.1	0.35	3500	1.08	1.8	405	75	6	16	2	8	1.8	3.0	66	0.01
KL38-08	499.1	502	0.138	1380	0.07	1.7	172	45	5	71	5	6	1.7	3.8	131	0.01
KL38-08	502	504.6	0.162	1620	0.05	0.1	21	10	0.01	15	0.01	5	0.5	2.1	260	0.01
KL38-08	504.6	508.1	0.102	1020	0.04	0.1	23	8	0.01	85	0.01	4	0.3	1.5	356	0.01
KL38-08	508.1	511.1	0.115	1150	0.12	0.7	16	18	0.01	27	1	12	1.4	1.5	159	0.01
KL38-08	511.1	514.1	0.117	1170	0.07	0.7	14	12	2	61	1	7	0.6	2.6	152	0.01
KL38-08	514.1	516.5	0.171	1710	0.13	0.8	21	11	6	460	4	8	1.8	4.0	153	0.01
KL38-08	516.5	520.1	0.3	3000	0.13	1.8	90	83	0.01	22	0.01	5	1.1	1.0	164	0.01
KL38-08	520.1	523.2	0.3	3000	0.07	1.4	44	18	2	29	0.01	3	0.3	1.4	138	0.01
KL38-08	523.2	526.1	0.159	1590	0.07	1	47	20	7	25	0.01	1	2	0.8	161	0.01
KL38-08	526.1	529.1	0.185	1850	0.05	1.1	40	37	1	29	0.01	2	1.6	0.9	172	0.01
KL38-08	529.1	532.1	0.22	2200	0.08	1.2	115	69	2	101	3	4	1.2	2.0	256	0.01
KL38-08	532.1	535	0.31	3100	0.23	2.3	92	67	110	120	5	10	8.4	4.1	170	0.01
KL38-08	535	538.1	0.25	2500	0.06	0.8	78	40	3	113	1	3	0.8	1.2	195	0.01
KL38-08	538.1	541.1	0.175	1750	0.02	0.7	62	66	11	30	0.01	4	1	1.2	307	0.01
KL38-08	541.1	544.1	0.211	2110	0.04	0.8	43	28	5	72	0.01	2	1.9	1.5	331	0.01
KL38-08	544.1	547.1	0.094	940	0.04	0.1	57	35	27	68	1	6	1.5	2.6	356	0.01
KL38-08	547.1	550.1	0.08	800	0.03	0.1	104	64	8	40	0.01	3	0.9	3.2	338	0.01
KL38-08	550.1	553.1	0.28	2800	0.1	0.8	31	28	9	202	1	3	2.5	4.2	307	0.01
KL38-08	553.1	556.1	0.147	1470	0.05	0.6	16	11	7	79	1	2	2.2	3.7	233	0.01
KL38-08	556.1	559.1	0.123	1230	0.07	0.1	44	27	6	26	1	3	0.8	2.8	198	0.01
KL38-08	559.1	562.1	0.16	1600	0.07	0.1	85	43	11	78	0.01	2	0.8	2.1	163	0.01
KL38-08	562.1	565.1	0.112	1120	0.32	1	184	190	200	185	3	37	11.3	7.1	132	0.01
KL38-08	565.1	568.1	0.012	120	0.04	0.1	81	52	11	85	0.01	2	0.7	1.7	185	0.01
KL38-08	568.1	571.4	0.033	330	0.1	0.6	730	780	61	97	0.01	11	1.8	4.0	300	0.01
KL38-08	571.4	574.1	0.053	530	0.17	0.5	320	190	130	203	1	34	6.8	3.8	278	0.01
KL38-08	574.1	577.1	0.115	1150	0.42	1.2	283	104	260	63	4	63	13.9	6.7	290	0.01
KL38-08	577.1	581.1	0.24	2400	0.63	2.1	78	67	800	198	3	95	64	8.6	203	0.01
KL38-08	581.1	584.1	0.0152	152	0.1	0.1	88	89	21	79	0.01	7	2.1	2.3	349	0.01
KL38-08	584.1	587.1	0.0246	246	0.15	0.1	430	86	37	82	5	8	4.1	7.9	284	0.01
KL38-08	587.1	590.1	0.052	520	0.09	0.1	158	94	61	34	0.01	3	1.7	1.4	343	0.01
KL38-08	590.1	593.1	0.063	630	0.1	0.6	117	62	37	50	0.01	2	1.5	1.7	179	0.01
KL38-08	593.1	596.1	0.104	1040	0.18	0.1	80	95	58	50	1	8	2.4	2.8	315	0.01
KL38-08	596.1	599	0.062	620	0.19	0.6	151	155	84	16	1	4	3.3	3.8	342	0.01
KL40-01	0	2.5	0.0042	42	0.02	0.1	241	92	8	2	0.01	1	1.6	0.0	15	0.1
KL40-01	2.5	5.5	0.0019	19	0.03	0.1	440	190	10	1	0.01	1	3.2	0.5	15	0.01
KL40-01	5.5	8.5	0.004	40	0.06	0.1	2400	252	25	5	0.01	1	24	1.5	15	0.19
KL40-01	8.5	10.8	0.005	50	0.03	0.7	540	190	19	6	1	1	10.1	2.1	15	0.01
KL40-01	10.8	14.5	0.005	50	0.04	0.1	410	178	20	6	1	1	2.9	1.4	16	0.01
KL40-01	14.5	17.5	0.0038	38	0.12	0.9	2800	460	36	29	1	1	12	2.7	16	0.18
KL40-01	17.5	20.5	0.0042	42	0.05	0.8	1300	411	20	3	2	1	4.2	2.5	15	0.17
KL40-01	20.5	23.5	0.0064	64	0.04	0.1	430	185	29	15	3	1	4.1	0.9	15	0.1
KL40-01	23.5	26.5	0.0117	117	0.02	0.1	215	190	25	40	2	1	0.8	0.7	18	0.01
KL40-01	26.5	29.5	0.0113	113	0.04	1	285	346	45	12	3	1	2.4	1.9	30	0.1

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL40-01	29.5	32.5	0.005		50	0.07	0.8	153	167	75	11	1	5.5	0.0	28	0.1	
KL40-01	32.5	35.5	0.0062		62	0.09	0.5	132	178	91	7	4	3.7	0.6	25	0.1	
KL40-01	35.5	37.9	0.0231		231	0.3	3.4	620	430	120	17	24	3	22	1.7	41	0.17
KL40-01	37.9	40.9	0.0081		81	0.1	1.2	241	181	97	20	8	2	6.2	1.0	27	0.12
KL40-01	40.9	44.5	0.0123		123	0.04	0.6	334	127	44	20	2	1	9	0.9	37	0.1
KL40-01	44.5	47.5	0.013		130	0.04	0.1	192	91	41	70	4	1	2.5	0.6	29	0.01
KL40-01	47.5	50.5	0.0042		42	0.39	0.8	520	145	110	29	6	2	12.6	1.7	37	0.16
KL40-01	50.5	53.5	0.0075		75	0.12	0.1	104	110	49	1	2	1	2.9	0.0	18	0.01
KL40-01	53.5	56.5	0.0039		39	0.03	0.1	76	89	26	1	0.01	1	0.8	0.6	20	0.01
KL40-01	56.5	59.5	0.005		50	0.02	0.1	132	217	17	6	0.01	1	0.5	1.9	24	0.01
KL40-01	59.5	62.5	0.0045		45	0.07	0.1	141	180	30	9	0.01	1	2.6	1.3	20	0.1
KL40-01	62.5	65.5	0.0048		48	0.14	0.1	215	134	38	5	0.01	1	4.4	1.4	24	0.11
KL40-01	65.5	68.5	0.004		40	0.08	0.1	157	148	42	2	0.01	1	2.1	1.3	28	0.01
KL40-01	68.5	71.5	0.0045		45	0.03	0.1	294	245	21	5	0.01	1	5.2	1.4	22	0.16
KL40-01	71.5	74.5	0.0052		52	0.03	0.1	262	191	14	10	1	2	9.8	1.4	23	0.01
KL40-01	74.5	77.5	0.0041		41	0.03	0.1	151	148	17	6	0.01	1	1.8	0.6	21	0.01
KL40-01	77.5	80.5	0.0055		55	0.04	0.1	135	224	17	13	0.01	1	4.6	1.3	23	0.01
KL40-01	80.5	83.5	0.0101		101	0.06	0.1	228	280	36	8	0.01	1	3.5	1.5	28	0.01
KL40-01	83.5	86.5	0.0172		172	0.77	59	7600	4300	150	6	1	1	14.6	182.0	29	0.15
KL40-01	86.5	89.5	0.0066		66	0.62	9	7300	4800	92	4	0.01	1	22	4.0	25	0.51
KL40-01	89.5	92.5	0.0045		45	0.39	0.1	197	151	63	5	0.01	1	3.1	3.8	26	0.1
KL40-01	92.5	95.5	0.0057		57	0.17	0.1	178	257	37	14	1	1	2.8	4.0	27	0.1
KL40-01	95.5	99.1	0.0035		35	0.24	0.9	188	1280	56	341	4	1	3.6	15.5	36	0.1
KL40-01	99.1	102.3	0.0116		116	0.02	1.1	530	187	17	27	5	1	0.5	5.4	17	0.01
KL40-01	102.3	105.7	0.0095		95	0.14	0.9	740	1130	46	9	3	1	5.5	10.5	32	0.01
KL40-01	105.7	107.5	0.059		590	0.15	3.6	5100	4100	79	13	16	1	12.3	13.3	38	0.1
KL40-01	107.5	110.5	0.0281		281	0.28	1.9	5200	530	160	147	18	3	14	11.3	65	0.28
KL40-01	110.5	113.5	0.0098		98	0.48	5	2080	890	160	2600	38	2	12.5	14.0	66	0.11
KL40-01	113.5	117.5	0.254		2540	2.31	5.6	1200	490	710	588	19	3	65	10.3	86	0.3
KL40-01	117.5	122	0.456		4560	2.92	7.7	341	287	810	670	18	2	315	13.2	180	0.51
KL40-01	122	125.7	0.302		3020	2.66	5.6	490	214	820	175	17	5	290	12.8	91	0.35
KL40-01	125.7	130.2	4.84		48400	3.57	15.5	7900	1550	970	67	176	4	240	56.5	213	1.45
KL40-01	130.2	134.1	0.0734		734	0.76	6.4	3700	1820	190	60	19	5	13.5	11.8	63	0.28
KL40-01	134.1	139.5	0.0109		109	0.47	2.3	1640	980	85	21	4	2	6.4	6.8	50	0.18
KL40-01	139.5	142	0.0262		262	0.64	11.2	12800	14400	150	70	4	2	30	30.0	36	0.44
KL40-01	142	145.5	0.0281		281	0.51	3.4	3400	880	67	78	8	2	44	7.5	46	0.42
KL40-01	145.5	148.6	0.59		5900	0.91	19.4	35300	1240	780	224	45	45	1070	40.5	41	2.88
KL40-01	148.6	152	0.264		2640	0.51	6.5	5800	410	260	385	16	30	12.8	32.2	23	0.3
KL40-01	152	155.2	0.35		3500	1.34	24	12400	5600	850	160	66	25	40	68.0	42	0.42
KL40-01	155.2	158	0.046		460	1.93	9.8	6400	4400	390	94	12	10	22	57.0	39	0.4
KL40-01	158	162.5	0.187		1870	1.08	8.5	4300	2040	170	55	17	5	40	15.9	43	0.52
KL40-01	162.5	166	0.017		170	0.72	12.7	8300	17500	110	106	2	1	34	22.3	38	0.6
KL40-01	166	168.5	0.0144		144	0.4	4.5	2600	5470	87	25	0.01	1	15.3	10.3	26	0.2
KL40-01	168.5	171.5	0.0193		193	0.28	3.2	1600	2510	40	40	2	1	8.1	8.4	28	0.11
KL40-01	171.5	174.7	0.0348		348	0.91	12.7	8500	4700	140	64	24	1	24	18.0	34	0.25
KL40-01	174.7	177.3	0.045		450	1.47	18.9	8600	8000	380	210	58	1	100	25.2	57	0.38
KL40-01	177.3	179.4	0.05		500	2.38	30	17100	22500	390	138	60	2	125	30.5	65	0.6
KL40-01	179.4	182.4	0.0334		334	1.92	17.7	7600	10100	320	124	28	1	50	19.0	55	0.52
KL40-01	182.4	184.3	0.058		580	1.48	55	29600	32100	490	73	18	2	72	28.5	61	0.56
KL40-01	184.3	188.5	0.054		540	2.7	47	19300	30000	1250	110	36	3	100	53.0	37	0.76
KL40-01	188.5	191.5	0.0336		336	1.37	32.1	15000	25700	540	67	13	2	78	30.0	22	0.7
KL40-01	191.5	194	0.0324		324	0.98	16.1	11000	10400	350	68	10	2	54	23.3	24	0.68
KL40-01	194	197.1	0.0179		179	1.34	12	1530	1340	480	339	8	5	40	13.3	40	0.96
KL40-01	197.1	200	0.0104		104	0.18	62	30500	23400	140	64	3	2	36	6.0	13	0.3
KL40-01	200	203.1	0.0248		248	0.33	15.4	7700	13100	390	101	2	1	15.9	5.0	28	0.14
KL40-01	203.1	206.1	0.0093		93	0.04	0.8	329	175	46	58	1	1	1.6	3.5	14	0.01
KL40-01	206.1	209.6	0.0138		138	0.16	12.1	4700	6200	65	62	2	1	28	2.0	23	0.34
KL40-01	209.6	211.5	0.078		780	0.51	7.8	3500	1460	220	130	12	9	9.6	8.0	29	0.33
KL40-01	211.5	215.5	0.173		1730	0.64	13.6	8800	1400	430	173	29	36	12	15.5	27	0.37
KL40-01	215.5	221.5	0.29		2900	0.84	25.2	22200	870	410	150	45	70	13.3	19.0	28	0.62
KL40-01	221.5	224.5	0.091		910	0.28	11.3	6600	2500	230	185	16	7	11.9	17.0	29	0.28
KL40-01	224.5	230.5	1.29		12900	2.53	69	72500	13500	3280	2880	118	120	50	139.5	86	0.9
KL40-02	0	3.5	0.0081		81	0.03	0.1	277	124	9	8	0.01	1	2.7	2.1	17	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL40-02	3.5	6.5	0.0045		45	0.01	0.1	329	147	11	6	0.01	1	2	2.6	15	0.01
KL40-02	6.5	9.5	0.0074		74	0.03	0.1	450	250	23	10	1	1	6.6	2.0	17	0.01
KL40-02	9.5	12.5	0.0075		75	0.05	0.8	560	184	21	4	2	2	7	1.8	18	0.12
KL40-02	12.5	15.5	0.0072		72	0.2	1.7	890	224	12	3	2	1	5.5	1.5	19	0.1
KL40-02	15.5	18.5	0.0289		289	0.1	1	309	374	13	9	2	1	3.6	1.5	16	0.01
KL40-02	18.5	20.7	0.0289		289	0.1	1	309	374	13	9	2	1	3.6	1.5	16	0.01
KL40-02	20.7	23.7	0.0248		248	0.06	0.8	257	210	26	6	2	1	3.4	1.4	17	0.01
KL40-02	23.7	26.7	0.0097		97	0.05	0.1	248	61	75	17	15	1	8.5	1.4	23	0.01
KL40-02	26.7	29.7	0.0129		129	0.04	0.1	238	91	60	9	8	1	5.2	1.5	22	0.01
KL40-02	29.7	32.7	0.0169		169	0.06	0.8	296	102	55	59	15	1	11.1	1.7	28	0.01
KL40-02	32.7	35.7	0.0364		364	0.06	1.2	140	68	64	187	13	2	9.8	1.8	24	0.01
KL40-02	35.7	38.7	0.0149		149	0.02	0.1	162	70	48	6	4	1	2.3	0.8	22	0.01
KL40-02	38.7	41.7	0.0182		182	0.06	0.1	143	98	67	13	7	1	5.4	1.0	22	0.01
KL40-02	41.7	44.7	0.0061		61	0.02	0.1	254	148	43	11	2	1	2.2	1.3	24	0.01
KL40-02	44.7	47.7	0.0155		155	0.05	0.1	520	159	51	9	1	1	5.2	1.9	26	0.01
KL40-02	47.7	50.7	0.0087		87	0.13	0.7	570	145	58	14	2	2	13.7	1.5	20	0.1
KL40-02	50.7	53.7	0.0083		83	0.03	0.7	287	98	70	96	4	1	1.8	1.9	31	0.01
KL40-02	53.7	56.7	0.008		80	0.1	0.9	710	279	86	13	14	2	2.9	2.7	30	0.1
KL40-02	56.7	59.7	0.0031		31	0.05	0.1	530	305	28	7	1	1	3.1	1.3	18	0.01
KL40-02	59.7	62.7	0.0152		152	0.13	0.8	840	173	100	6	0.01	1	6.8	2.2	17	0.13
KL40-02	62.7	65.7	0.0034		34	0.07	0.1	256	156	36	4	1	1	2.3	1.4	20	0.01
KL40-02	65.7	68.7	0.0107		107	0.09	0.6	358	106	50	6	2	1	3.5	2.1	22	0.1
KL40-02	68.7	71.7	0.064		640	0.18	2.8	1280	700	150	31	17	3	48	10.8	48	0.18
KL40-02	71.7	74.7	0.0051		51	0.26	1.2	510	266	84	9	0.01	1	16	6.9	42	0.16
KL40-02	74.7	77.7	0.0079		79	0.31	1.8	2100	490	100	9	5	3	12.8	5.3	40	0.13
KL40-02	77.7	80.7	0.0053		53	0.14	0.8	1020	265	83	13	4	1	11.5	4.5	25	0.01
KL40-02	80.7	83.7	0.0181		181	0.04	0.6	810	163	61	22	3	1	9.8	2.8	35	0.01
KL40-02	83.7	86.7	0.031		310	0.41	4.2	1140	550	320	72	110	7	42	37.7	88	0.1
KL40-02	86.7	89.7	0.0075		75	0.06	0.1	232	84	110	275	1	4	8.6	1.6	66	0.01
KL40-02	89.7	93.1	0.0056		56	0.12	0.1	680	132	64	313	4	4	4.9	3.9	70	0.01
KL40-02	93.1	96.3	0.0095		95	0.15	0.1	610	255	37	35	1	5	1.9	3.3	57	0.1
KL40-02	96.3	99.3	2.67		26700	1.68	27	750	430	1310	143	281	70	1080	57.0	215	3.76
KL40-02	99.3	102.3	0.2		2000	1.27	25	28300	12700	130	330	7	5	30	15.0	251	2.1
KL40-02	102.3	105.3	0.0257		257	1.83	58	46400	34900	210	480	2	5	44	24.0	279	4.24
KL40-02	105.3	108.3	0.066		660	0.71	20.3	660	7100	160	223	150	4	26	10.0	145	0.42
KL40-02	108.3	111.3	0.032		320	0.57	12.1	1150	1290	100	720	75	3	11.6	7.0	127	0.28
KL40-02	111.3	114.3	0.152		1520	0.76	14.3	18200	7400	370	570	155	5	82	18.0	99	0.48
KL40-02	114.3	117.3	0.073		730	1.53	15.1	730	400	110	620	29	4	304	5.3	255	0.64
KL40-02	117.3	120.3	0.048		480	1.75	13.6	381	258	160	1610	72	6	94	8.3	312	0.5
KL40-02	120.3	122.6	0.57		5700	4.52	188	68000	55400	1690	2090	590	18	64	43.5	188	18.9
KL40-02	122.6	125.6	0.055		550	0.8	8.3	35000	6800	170	128	18	7	14.9	30.5	65	0.46
KL40-02	125.6	128.6	0.0258		258	0.31	1.2	1310	317	100	39	3	3	3.5	4.3	24	0.13
KL40-02	128.6	131.6	0.0065		65	0.13	0.1	2640	540	25	32	2	2	1.7	3.3	22	0.1
KL40-02	131.6	134.6	0.042		420	0.27	3.7	10600	3700	90	78	19	4	7	23.5	30	0.42
KL40-02	134.6	137.6	0.0386		386	0.22	1.6	4230	1210	60	58	8	3	2.6	5.8	30	0.25
KL40-02	137.6	140.6	0.012		120	0.07	1.5	1620	347	15	42	45	2	0.7	4.5	26	0.01
KL40-02	140.6	143.6	0.0224		224	0.1	1	5360	308	34	33	7	4	1.7	5.5	26	0.17
KL40-02	143.6	146.6	0.0123		123	0.06	0.1	2760	151	14	30	6	2	0.01	3.0	24	0.15
KL40-02	146.6	149.6	0.0087		87	0.1	0.8	1560	470	21	63	5	2	1.6	2.8	27	0.01
KL40-02	149.6	152.6	0.052		520	0.21	3.2	14700	2200	160	89	9	6	7.6	12.0	35	0.28
KL40-02	152.6	155.6	0.0113		113	0.07	1.1	3340	460	20	24	8	2	1.7	2.8	30	0.1
KL40-02	155.6	157.7	0.059		590	0.2	2.4	14000	500	150	39	23	9	3.6	13.5	23	0.14
KL40-02	157.7	160.6	0.042		420	0.21	1.5	1450	192	98	3030	53	8	2.1	6.0	50	0.01
KL40-02	160.6	163.5	0.0218		218	0.34	2.3	500	393	75	2340	31	8	2.7	10.1	33	0.01
KL40-02	163.5	166.5	0.0265		265	0.11	0.8	1290	116	55	46	4	4	1.8	2.3	13	0.15
KL40-02	166.5	169.5	0.0128		128	0.09	1.1	1260	213	23	25	4	2	0.9	2.5	12	0.12
KL40-02	169.5	172.5	0.0075		75	0.15	2.4	3350	1170	34	18	7	2	1	4.5	13	0.18
KL40-02	172.5	175.5	0.0115		115	0.12	1.2	530	670	24	17	3	3	1.6	2.5	13	0.1
KL40-02	175.5	178.5	0.0137		137	0.11	1.2	2450	880	37	14	2	3	1.2	1.9	14	0.25
KL40-02	178.5	181.5	0.0095		95	0.1	1	1940	870	23	18	2	2	0.9	2.5	11	0.23
KL40-02	181.5	184.5	0.0224		224	0.25	5.1	8300	5100	42	30	7	4	4.7	14.8	14	0.38
KL40-02	184.5	187.5	0.0253		253	0.36	2.4	2520	880	71	31	10	3	3.2	5.8	20	0.23
KL40-02	187.5	190.5	0.0378		378	0.16	0.8	910	168	79	40	4	4	2.3	2.3	21	0.1

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL40-02	190.5	194.1	0.29	2900	0.34	5.4	4010	1430	830	20	5	16	9.4	5.8	23	0.16
KL40-02	194.1	197.7	0.13	1300	0.25	5	5440	2520	290	20	20	4	5.3	6.5	23	0.01
KL40-02	197.7	201.2	0.4	4000	0.79	5.3	4990	327	740	21	6	40	6.9	11.3	42	0.24
KL40-02	201.2	204.6	0.4	4000	1.01	5.3	4850	292	680	24	7	38	5.9	12.5	41	0.23
KL40-02	204.6	207.6	0.18	1800	1.86	2.9	3210	620	640	7	8	4	14.4	10.2	93	0.01
KL40-02	207.6	210.6	0.44	4400	1.36	4.6	9000	252	300	9	19	16	12.2	9.0	73	0.01
KL40-02	210.6	213.6	0.83	8300	1.64	4.3	10600	1500	840	303	28	34	7	27.0	146	0.01
KL40-02	213.6	216.6	0.77	7700	0.7	3	7600	1100	1730	353	13	41	3.9	29.0	201	0.01
KL40-02	216.6	219.6	0.37	3700	0.36	2.1	750	480	1130	580	7	30	11	14.0	242	0.15
KL40-02	219.6	222.6	0.93	9300	0.42	4.1	1600	640	2640	1170	7	45	5.8	19.0	352	0.19
KL40-02	222.6	225.6	0.64	6400	0.52	3.3	1710	570	2040	500	8	14	2	17.0	209	0.16
KL40-02	225.6	228.6	0.79	7900	1.28	2.1	154	32	1	14	0.01	16	0.01	5.0	131	0.01
KL40-02	228.6	231.6	0.78	7800	1.1	9.1	560	203	1330	50	28	30	2.9	24.5	238	0.01
KL40-02	231.6	234.6	2.05	20500	0.88	9.6	417	218	910	376	7	65	1	33.0	263	0.01
KL40-02	234.6	237.6	3.21	32100	1.12	9.5	600	323	1680	5170	4	38	3	26.0	174	0.01
KL40-02	237.6	240.6	1.3	13000	1.12	10.1	810	325	2180	115	32	60	5.9	21.5	219	0.1
KL40-02	240.6	243.6	2.24	22400	1.1	11.8	400	286	540	562	18	80	19	36.0	157	0.01
KL40-02	243.6	246.6	2.27	22700	0.82	8.2	183	113	900	310	8	70	2.1	43.5	204	0.01
KL40-02	246.6	249.6	2.68	26800	1.26	9	210	148	1980	219	7	36	2	36.0	139	0.15
KL40-02	249.6	252.6	2.14	21400	2.96	25.1	600	270	1870	1250	36	31	2.6	19.0	99	0.01
KL40-02	252.6	255.6	2	20000	2.06	11.5	1480	580	2050	74	29	62	3.5	23.5	140	0.13
KL40-02	255.6	258.6	1.96	19600	1.8	10.6	320	560	2130	88	25	36	4.2	31.0	133	0.18
KL40-02	258.6	261.6	0.98	9800	2.28	11	137	282	1290	152	39	67	1.8	24.5	117	0.01
KL40-02	261.6	264.6	0.88	8800	1.3	2.8	77	85	1720	250	23	70	3.1	55.5	194	0.1
KL40-02	264.6	267.6	1.5	15000	1.12	4.9	305	165	2030	321	15	38	4.2	17.0	218	0.18
KL40-02	267.6	270.6	1.24	12400	1.04	4	105	135	1860	76	18	40	5.7	38.5	178	0.25
KL40-02	270.6	273.6	0.58	5800	1.48	4.3	390	225	1430	68	72	8	4.4	49.8	164	0.13
KL40-02	273.6	276.6	1.02	10200	1.46	4.6	412	182	1630	94	191	2	4.8	40.5	149	0.22
KL40-02	276.6	279.6	3.22	32200	1.48	19	580	760	6560	45	136	2	7.5	43.0	62	0.94
KL40-02	279.6	282.6	3.34	33400	1.64	13.6	530	410	6900	26	53	3	6.9	34.0	142	0.72
KL40-02	282.6	285.6	2.5	25000	2.4	6.4	2300	710	1820	152	22	24	3.1	54.0	163	0.58
KL40-02	285.6	288.6	1.8	18000	2.62	3.8	480	140	560	65	17	34	1.6	56.0	142	0.62
KL40-02	288.6	291.6	0.52	5200	1	2	163	129	170	41	25	4	3.6	54.0	145	0.29
KL40-02	291.6	294.6	0.38	3800	0.88	2.8	430	143	570	53	29	2	2.8	17.8	148	0.22
KL40-02	294.6	297.6	2.4	24000	2.24	9	2050	145	1420	11	62	1	3.3	23.0	78	0.62
KL40-02	297.6	300.6	2.13	21300	1.82	13.5	3300	540	340	83	96	1	7.4	8.5	146	0.18
KL40-02	300.6	303.6	0.26	2600	1.3	5.8	5460	1040	670	35	35	2	6.4	33.4	141	0.1
KL40-02	303.6	306.6	2.4	24000	1.52	11.1	2200	430	200	6	54	1	4.4	23.0	185	0.56
KL40-02	306.6	309.6	1.4	14000	2.38	7.4	146	185	260	3	24	1	1.7	8.5	178	0.44
KL40-02	309.6	312.6	2.83	28300	1.44	6.3	113	91	70	13	19	1	1.7	8.0	146	0.77
KL40-02	312.6	315.6	0.96	9600	1.64	2	127	103	180	8	23	1	1.7	22.0	162	0.32
KL40-02	315.6	318.6	0.75	7500	1.16	4.3	2380	560	130	48	23	5	3.9	34.0	160	0.35
KL40-02	318.6	321.6	1.31	13100	1.08	2.8	280	69	150	30	37	5	0.8	49.0	162	0.37
KL40-02	321.6	324.6	1.87	18700	0.92	5.6	73	37	42	45	16	18	1.4	47.0	203	0.24
KL40-02	324.6	327.6	1.05	10500	0.59	4.1	117	54	33	62	6	39	0.9	33.5	145	0.19
KL40-02	327.6	330.6	1.49	14900	0.77	3.7	60	43	33	157	1	72	0.7	32.0	148	0.18
KL40-02	330.6	333.6	2.25	22500	0.95	7.3	65	30	21	61	7	79	0.6	54.0	34	0.23
KL40-02	333.6	336.6	0.83	8300	0.59	3.2	41	31	30	71	7	13	0.8	36.0	166	0.18
KL40-02	336.6	339.6	1.51	15100	0.72	5.1	46	26	26	77	8	14	0.6	25.0	41	0.27
KL40-02	339.6	342.6	1.11	11100	0.84	2.3	58	30	33	46	7	30	0.8	34.5	147	0.32
KL40-02	342.6	345.6	0.36	3600	0.58	1.5	52	35	50	107	6	15	0.7	29.9	45	0.19
KL40-02	345.6	348.6	1.34	13400	0.94	3.5	65	54	83	60	18	12	2	29.5	130	0.32
KL40-02	348.6	351.6	1.26	12600	1.08	4.5	68	59	35	40	18	14	0.7	28.5	57	0.31
KL40-02	351.6	354.6	1.4	14000	1.7	3	83	66	39	35	16	40	0.6	41.0	173	0.18
KL40-02	354.6	357.6	1.19	11900	1.2	1.8	365	89	82	49	6	57	1.1	20.0	42	0.14
KL40-02	357.6	360.6	1.98	19800	1.2	2.7	1280	290	56	47	6	28	0.6	14.5	38	0.13
KL40-02	360.6	363.6	1.94	19400	1.82	4.3	990	240	54	188	7	58	0.9	14.0	34	0.23
KL40-02	363.6	366.6	1	10000	1.28	2.7	1310	440	160	116	15	48	1.2	18.5	52	0.11
KL40-02	366.6	369.6	0.86	8600	1.12	2.4	3800	2100	220	153	18	72	1.3	19.5	157	0.01
KL40-02	369.6	372.6	1.21	12100	1.4	3	4180	2700	210	128	16	74	1.1	19.0	65	0.01
KL40-02	372.6	375.6	1.09	10900	1.42	3.4	430	129	150	149	27	70	1.3	26.0	143	0.01
KL40-02	375.6	378.6	0.99	9900	1.28	5.3	430	175	400	56	21	60	2.8	17.5	126	0.01
KL40-02	378.6	381.6	0.97	9700	0.9	11.1	570	1430	110	108	13	35	1.6	27.0	101	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL40-02	381.6	384.6	1.26	12600	1.12	7.7	1610	3600	110	175	13	41	3.9	18.5	53	0.01
KL40-02	384.6	387.6	2.46	24600	1.6	9	1240	570	110	314	7	42	2.3	19.0	126	0.01
KL40-02	387.6	390.6	1.72	17200	1.5	8.7	1190	1040	140	401	14	43	2.8	23.8	49	0.01
KL40-02	390.6	393.6	4.82	48200	3.31	11.3	1170	305	56	240	5	75	1.6	26.0	158	0.01
KL40-02	393.6	396.6	1.53	15300	1.36	6	394	349	58	353	4	49	1.8	17.5	41	0.01
KL40-02	396.6	399.6	1.52	15200	2.35	9.4	2100	2800	96	102	8	22	5.6	13.5	84	0.01
KL40-02	399.6	402	0.6	6000	0.96	5.3	1400	1450	120	87	15	13	2.3	7.0	143	0.01
KL40-02	402	406.7	0.57	5700	0.92	3.9	1700	1110	180	140	33	18	3.9	9.4	71	0.01
KL40-02	406.7	409.2	0.394	3940	0.4	4.9	1500	810	69	105	34	11	2.1	29.5	204	0.01
KL40-02	409.2	413.7	0.285	2850	0.51	2.4	1400	362	79	210	13	15	1.4	21.8	181	0.01
KL40-02	413.7	423.2	0.78	7800	0.76	6.8	760	365	210	171	17	9	1.6	12.4	161	0.1
KL40-02	423.2	426.4	0.344	3440	0.68	6	230	68	170	130	39	12	0.4	25.5	42	0.01
KL40-02	426.4	431.6	0.64	6400	1.06	4.3	850	217	1180	227	15	10	0.7	21.3	140	0.01
KL40-02	431.6	451.3	0.7	7000	1.52	14.9	2090	1730	690	519	15	21	5.4	3.9	45	0.01
KL40-02	451.3	456.5	0.0137	137	0.18	0.8	102	74	33	35	16	3	1.1	1.6	17	0.01
KL40-02	456.5	459.5	0.0192	192	0.07	0.1	71	18	30	15	0.01	1	0.4	1.8	17	0.01
KL40-02	459.5	462.7	0.0201	201	0.26	1.1	1230	590	91	12	2	1	2.9	4.0	26	0.01
KL40-02	462.7	465	0.0298	298	0.17	0.6	353	174	55	60	9	1	1.9	3.2	21	0.01
KL40-02	465	467.9	0.0051	51	0.04	0.1	43	14	18	6	0.01	1	0.2	1.6	18	0.01
KL40-02	467.9	471.8	0.0081	81	0.06	0.1	148	74	27	7	0.01	1	0.6	1.9	15	0.01
KL40-02	471.8	474.7	0.0037	37	0.05	0.1	54	18	7	2	0.01	1	0.2	1.0	13	0.01
KL40-02	474.7	477.7	0.0094	94	0.03	0.1	40	20	26	4	0.01	1	0.01	1.3	12	0.01
KL40-02	477.7	480.7	0.0062	62	0.01	0.1	57	12	12	3	0.01	1	0.01	0.9	12	0.01
KL40-02	480.7	483.5	0.0056	56	0.03	0.1	43	8	11	1	0.01	1	0.01	1.0	14	0.01
KL40-02	483.5	486.7	0.0042	42	0.05	0.1	147	112	26	3	0.01	1	0.7	2.6	10	0.01
KL40-02	486.7	489.2	0.0043	43	0.01	0.1	49	6	16	1	0.01	1	0.2	0.8	15	0.01
KL40-02	489.2	492.7	0.0052	52	0.01	0.1	366	30	25	2	0.01	1	0.3	0.8	16	0.01
KL40-02	492.7	494.9	0.0046	46	0.02	0.1	100	25	24	4	0.01	1	0.2	0.7	16	0.01
KL40-02	494.9	497.9	0.0047	47	0.02	0.1	200	87	22	5	2	1	0.4	0.8	13	0.01
KL40-02	497.9	501.7	0.038	380	0.2	0.5	380	179	61	90	8	1	1.6	3.0	23	0.01
KL40-02	501.7	504.8	0.0044	44	0.01	0.1	44	14	9	4	0.01	1	0.01	0.8	14	0.01
KL40-02	504.8	507.8	0.0039	39	0.02	0.1	49	12	11	4	0.01	1	0.01	0.7	18	0.01
KL40-02	507.8	512.9	0.016	160	0.02	0.1	60	14	8	27	0.01	1	0.01	1.1	16	0.01
KL40-02	512.9	515.5	0.042	420	0.04	0.1	51	12	9	80	0.01	1	0.01	1.4	12	0.01
KL40-02	515.5	519	0.0033	33	0.01	0.1	37	9	3	4	0.01	1	0.01	0.6	14	0.01
KL40-02	519	522.7	0.0039	39	0.05	0.1	167	15	14	3	0.01	1	0.2	0.6	14	0.01
KL40-02	522.7	525.7	0.006	60	0.04	1.1	231	510	28	10	6	1	1.8	4.5	13	0.01
KL40-02	525.7	528.8	0.0074	74	0.1	0.1	61	33	12	8	7	1	0.3	0.7	15	0.01
KL40-02	528.8	531.7	0.0203	203	0.02	0.1	70	15	30	21	0.01	1	0.2	1.4	17	0.01
KL40-02	531.7	534.7	0.0136	136	0.05	0.1	82	27	24	14	0.01	1	0.4	1.3	17	0.01
KL40-02	534.7	537.4	0.0038	38	0.01	0.1	45	10	5	3	0.01	1	0.01	0.0	15	0.01
KL40-02	537.4	540.3	0.0098	98	0.03	0.1	69	33	19	8	0.01	1	0.2	1.0	18	0.01
KL40-02	540.3	543.3	0.0211	211	0.03	0.1	47	1	27	5	0.01	6	0.2	1.8	41	0.01
KL40-02	543.3	546.3	0.0025	25	0.01	0.1	14	8	0.01	4	0.01	1	0.01	0.0	17	0.01
KL40-02	546.3	549.7	0.0212	212	0.21	2.1	2040	700	74	7	0.01	1	6.8	2.3	17	0.01
KL40-02	549.7	552.7	0.005	50	0.04	0.1	176	314	26	7	3	1	1.4	3.2	15	0.01
KL40-02	552.7	555.7	0.0021	21	0.04	0.1	26	8	14	5	0.01	1	0.2	1.5	20	0.01
KL40-02	555.7	558.7	0.0032	32	0.02	0.1	44	28	13	4	0.01	1	0.4	0.8	15	0.01
KL40-02	558.7	561.7	0.0109	109	0.01	0.1	60	15	19	2	0.01	1	1.5	0.8	14	0.01
KL40-02	561.7	564.8	0.0033	33	0.1	0.1	57	33	18	10	0.01	1	0.2	0.6	18	0.01
KL40-02	564.8	567.7	0.004	40	0.02	0.1	22	23	12	2	0.01	1	0.7	0.7	19	0.01
KL40-02	567.7	570.7	0.0066	66	0.03	0.1	46	19	12	4	0.01	1	0.6	0.0	16	0.01
KL40-02	570.7	573.7	0.0023	23	0.04	0.1	33	23	13	3	0.01	1	0.7	0.0	20	0.01
KL40-02	573.7	576.7	0.0018	18	0.03	0.1	55	44	11	3	0.01	1	0.6	0.0	18	0.01
KL40-02	576.7	579.7	0.0077	77	0.03	0.1	26	19	8	3	0.01	1	0.01	0.0	15	0.01
KL40-02	579.7	582.7	0.0186	186	0.06	0.9	132	185	34	1	0.01	1	14.2	1.0	18	0.01
KL40-02	582.7	585.7	0.075	750	0.07	0.5	91	36	21	1	1	1	2.1	1.7	14	0.01
KL40-02	585.7	588.7	0.0387	387	0.06	0.7	191	46	56	1	0.01	1	12	1.4	18	0.01
KL40-02	588.7	591.3	0.0109	109	0.09	0.1	71	16	16	4	0.01	1	0.4	1.4	15	0.01
KL40-02	591.3	594.4	0.0024	24	0.03	0.1	21	14	6	1	0.01	1	0.2	0.6	12	0.01
KL40-03	0	3	0.0061	61	0.03	0.5	276	103	12	11	2	1	3.4	1.5	17	0.01
KL40-03	3	5.7	0.0192	192	0.04	0.6	224	127	18	23	7	1	1.3	2.8	21	0.01
KL40-03	5.7	8.7	0.0043	43	0.01	0.9	404	160	15	4	1	1	2.3	1.3	20	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL40-03	8.7	11.7	0.0069		69	0.03	0.8	470	231	19	8	2	1	3	1.5	21	0.01
KL40-03	11.7	14.7	0.0053		53	0.13	1.2	760	189	18	3	2	1	3.9	1.5	22	0.2
KL40-03	14.7	17.7	0.0105		105	0.12	1.6	1420	364	32	14	17	1	3	4.3	18	0.15
KL40-03	17.7	20.7	0.0305		305	0.05	1.5	840	128	47	16	11	2	16.6	2.7	24	0.1
KL40-03	20.7	23.7	0.0065		65	0.01	0.9	355	204	21	10	3	2	2.4	2.3	18	0.01
KL40-03	23.7	26.7	0.0266		266	0.09	1.9	1240	194	75	49	31	2	8.5	4.8	30	0.11
KL40-03	26.7	29.7	0.0159		159	0.08	1.8	500	264	50	64	18	2	16	2.3	27	0.14
KL40-03	29.7	32.7	0.0272		272	0.18	1.2	460	268	47	93	22	2	2.8	5.9	22	0.01
KL40-03	32.7	35.7	0.0125		125	0.04	0.6	500	102	52	32	8	1	6.4	2.0	28	0.01
KL40-03	35.7	38.7	0.0156		156	0.03	1	295	126	31	22	11	1	2.5	2.0	18	0.01
KL40-03	38.7	41.7	0.0133		133	0.14	0.8	1230	105	48	55	12	1	4.4	3.0	20	0.1
KL40-03	41.7	44.7	0.05		500	0.08	0.7	410	108	76	349	8	4	12.5	3.0	23	0.13
KL40-03	44.7	47.7	0.103		1030	0.1	2.1	1850	138	130	78	30	4	34	5.3	28	0.26
KL40-03	47.7	50.7	0.0212		212	0.08	1.7	1880	340	73	57	19	3	12.4	4.3	23	0.11
KL40-03	50.7	53.7	0.0107		107	0.05	1	1240	210	53	24	6	1	10.5	2.5	25	0.01
KL40-03	53.7	56.7	0.075		750	0.08	2.1	1850	242	260	13	15	5	10.4	5.8	18	0.48
KL40-03	56.7	59	0.0134		134	0.04	0.6	670	217	45	16	3	1	6.4	3.0	20	0.1
KL40-03	59	61.5	0.072		720	0.09	1.9	1510	203	44	38	9	3	2.8	3.8	37	0.11
KL40-03	61.5	63.5	0.0152		152	0.1	0.9	285	105	64	46	4	9	3.4	12.0	18	0.1
KL40-03	63.5	65.4	0.0123		123	0.06	3.1	165	700	78	8	7	9	3	7.3	18	0.01
KL40-03	65.4	68.5	0.0306		306	0.08	5.7	410	840	66	9	30	8	3.8	4.8	18	0.1
KL40-03	68.5	71.6	0.0279		279	0.13	1.7	384	296	93	11	13	6	5.4	16.5	23	0.1
KL40-03	71.6	74.7	0.0242		242	0.19	1.9	435	1000	210	16	3	9	9	9.8	18	0.13
KL40-03	74.7	77.7	0.39		3900	0.24	41	68600	43200	200	42	25	8	175	67.8	17	0.85
KL40-03	77.7	80.7	0.14		1400	0.41	40	48100	49100	170	25	30	6	50	140.0	65	0.27
KL40-03	80.7	83.7	0.0354		354	0.2	5.5	9400	7900	71	35	18	6	9.8	23.5	17	0.26
KL40-03	83.7	86.7	0.047		470	0.17	2.2	700	350	82	14	22	9	5.3	33.5	22	0.1
KL40-03	86.7	89.7	0.0154		154	0.04	1.8	700	1310	55	44	3	11	3	4.5	30	0.01
KL40-03	89.7	92.7	0.0174		174	0.07	0.7	500	125	58	40	34	10	3.4	14.6	22	0.01
KL40-03	92.7	95.7	0.0064		64	0.07	0.6	172	58	58	6	3	12	1.9	4.8	24	0.01
KL40-03	95.7	98.8	0.0194		194	0.13	1.4	223	140	130	1070	14	2	4.1	10.5	21	0.01
KL40-03	98.8	101.6	0.11		1100	0.15	1.7	231	124	180	841	18	8	23.5	13.0	18	0.01
KL40-03	101.6	104.7	0.062		620	0.11	1.6	307	198	69	286	11	3	8.8	4.8	23	0.01
KL40-03	104.7	106.7	0.0204		204	0.4	1.5	500	208	62	73	6	3	4.5	8.0	24	0.1
KL40-03	106.7	109	1.91		19100	1.44	6.1	720	480	410	760	67	4	122	17.5	134	0.44
KL40-03	109	111.2	1.5		15000	1.4	2.8	326	376	190	1780	7	2	42	9.5	137	0.27
KL40-03	111.2	113.7	0.281		2810	0.6	2.7	1700	520	110	111	1	1	52	4.8	182	0.47
KL40-03	113.7	116.4	0.062		620	0.93	1.9	1130	530	78	187	4	2	28	3.5	85	0.15
KL40-03	116.4	119.7	0.0309		309	0.63	1.5	1380	375	78	232	3	1	20	4.0	191	0.21
KL40-03	119.7	122.7	0.0174		174	0.69	2.6	550	267	130	220	14	2	10.5	7.5	195	0.24
KL40-03	122.7	125.7	0.0184		184	1.28	1.8	650	245	240	3920	8	6	15.7	16.3	174	0.62
KL40-03	125.7	128.7	0.04		400	2.12	4.9	3000	9600	430	2900	26	5	22	13.9	234	0.68
KL40-03	128.7	131.2	0.065		650	1.18	5.2	16600	2700	520	830	31	15	29	22.0	210	0.78
KL40-03	131.2	134	0.21		2100	1.75	40	69500	15200	500	568	113	13	45	46.0	113	1.85
KL40-03	134	136.7	0.086		860	0.31	6.5	24400	3900	120	123	54	4	12.8	20.9	32	0.37
KL40-03	136.7	138.7	0.0206		206	0.28	2.5	7500	780	53	113	56	2	3.2	6.3	27	0.33
KL40-03	138.7	141.7	0.014		140	0.16	2	5500	640	42	67	20	1	2.8	8.0	24	0.24
KL40-03	141.7	145.7	0.0152		152	0.12	1.2	4300	236	43	115	4	2	3.9	12.8	25	0.22
KL40-03	145.7	147.7	0.0184		184	0.1	0.9	2100	158	76	184	4	2	3.2	4.0	21	0.16
KL40-03	147.7	149.7	0.0131		131	0.05	0.6	2200	48	66	216	14	2	4.9	4.5	26	0.01
KL40-03	149.7	152.4	0.0122		122	0.12	1.2	2800	77	56	1180	16	8	2	3.3	24	0.01
KL40-03	152.4	155.7	0.056		560	0.23	2.9	5600	2400	72	180	16	6	4.6	12.5	21	0.18
KL40-03	155.7	158.7	0.0276		276	0.31	1.6	1700	160	110	172	12	2	6.1	3.8	25	0.29
KL40-03	158.7	161.7	0.0284		284	0.24	2.5	2100	302	100	60	75	2	3.3	6.3	20	0.21
KL40-03	161.7	164	0.0192		192	0.17	1.6	2200	278	50	108	21	3	1.4	5.0	18	0.24
KL40-03	164	167.7	0.0208		208	0.2	1.5	2800	440	40	40	33	1	2.4	4.8	14	0.2
KL40-03	167.7	170.7	0.0237		237	0.21	2.4	1800	406	72	27	17	1	2.8	5.3	21	0.26
KL40-03	170.7	173.7	0.0184		184	0.2	1	1440	151	55	26	16	1	1.7	5.5	18	0.16
KL40-03	173.7	175.8	0.0122		122	0.21	0.6	1640	75	43	28	16	2	2.7	2.8	16	0.14
KL40-03	175.8	177.6	0.034		340	0.73	1.7	4700	199	190	29	16	18	11.7	6.5	17	0.58
KL40-03	177.6	179.7	0.32		3200	1.43	3.7	11700	1640	390	104	116	43	35	16.8	43	0.68
KL40-03	179.7	182.3	1.73		17300	2.27	3.2	650	124	390	270	3	45	17	20.0	67	0.18
KL40-03	182.3	185.7	1.02		10200	1.84	3.3	247	37	59	98	5	15	11.4	18.0	61	0.12

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL40-03	185.7	188.7	1.39	13900	2.04	5.7	980	93	1170	285	9	77	48	74.0	107	0.23
KL40-03	188.7	191.7	1.41	14100	1.8	2.7	328	72	560	337	13	86	25.3	83.0	85	0.16
KL40-03	191.7	194.7	4.16	41600	2.23	5.3	268	40	46	343	1	94	6.3	50.0	46	0.01
KL40-03	194.7	197.7	1.25	12500	1.17	2.4	340	62	34	191	3	40	3.9	14.5	33	0.01
KL40-03	197.7	200.7	0.471	4710	0.65	1.7	167	28	25	28	3	37	2.6	15.3	20	0.01
KL40-03	200.7	203.7	0.7	7000	1.18	2.4	198	116	56	31	1	50	3.6	20.3	38	0.01
KL40-03	203.7	206.7	0.299	2990	0.64	0.8	154	61	93	31	1	33	3.2	17.8	36	0.01
KL40-03	206.7	209.7	0.99	9900	1.02	2.7	186	21	32	124	0.01	48	2.4	9.3	27	0.01
KL40-03	209.7	212.7	1.35	13500	1.6	4.7	145	18	25	25	1	40	3.8	14.0	28	0.01
KL40-03	212.7	215.7	3.55	35500	3.51	11.5	4200	281	170	620	0.01	115	8.5	35.0	60	0.01
KL40-03	215.7	218.7	2.71	27100	2.62	8	2800	214	260	230	0.01	79	8.8	17.0	46	0.01
KL40-03	218.7	221.7	1.14	11400	1.37	2.8	115	45	270	27	0.01	15	6.4	19.0	45	0.01
KL40-03	221.7	224.7	0.152	1520	0.24	1	15100	4500	260	521	0.01	13	5.8	6.5	142	0.1
KL40-03	224.7	227.7	0.56	5600	0.68	1.2	175	24	58	252	0.01	18	3.4	14.5	26	0.1
KL40-03	227.7	230.7	2.1	21000	1.46	4.6	268	410	200	200	0.01	45	6.3	14.0	30	0.01
KL40-03	230.7	233.7	1.51	15100	1.12	12.7	1800	1100	1430	132	6	40	11.4	10.5	48	0.33
KL40-03	233.7	236	1.22	12200	4.83	51	4300	27600	2670	216	62	44	40	48.0	64	1.15
KL40-03	236	239.5	0.86	8600	1.4	74	12300	50400	1790	508	138	17	52	25.2	198	1.43
KL40-03	239.5	242.7	0.47	4700	0.52	4.4	6400	5600	500	1440	4	7	4	9.2	107	0.28
KL40-03	242.7	245.7	0.28	2800	0.6	2.5	16200	5400	340	450	1	14	7.3	7.7	199	0.34
KL40-03	245.7	248.7	2.17	21700	2.52	5.1	174	68	200	50	0.01	46	6.6	14.8	37	0.11
KL40-03	248.7	251.7	0.17	1700	0.11	0.8	5500	330	180	790	0.01	16	2.7	3.5	55	0.01
KL40-03	251.7	254.7	1.09	10900	0.71	4.2	1060	580	620	195	1	31	8.5	10.4	41	0.12
KL40-03	254.7	257.7	1.07	10700	0.44	2.7	690	670	1170	600	0.01	34	7.5	11.5	58	0.72
KL40-03	257.7	260.2	1.7	17000	1.21	4.6	410	470	280	230	2	48	4.5	12.0	48	0.3
KL40-03	260.2	263.7	1.48	14800	0.99	4.6	368	330	160	448	1	54	5	12.5	52	0.14
KL40-03	263.7	266.7	1	10000	0.37	3.3	580	396	96	156	1	35	1.3	9.8	28	0.01
KL40-03	266.7	269.7	1.07	10700	0.46	3.6	302	224	190	104	1	36	4.2	8.0	32	0.1
KL40-03	269.7	272.7	0.6	6000	0.63	3.2	351	430	140	64	3	58	7.2	8.8	30	0.01
KL40-03	272.7	275.7	0.89	8900	0.48	2.6	126	99	160	50	0.01	38	5	5.5	31	0.01
KL40-03	275.7	278.7	1.07	10700	0.37	6.8	520	380	110	180	0.01	34	6.6	6.1	29	0.01
KL40-03	278.7	282	1.25	12500	0.54	2.8	237	150	180	61	1	25	5.6	11.0	18	0.01
KL40-03	282	284.7	1.78	17800	1.01	3.3	291	375	340	86	4	16	7.1	16.0	29	0.13
KL40-03	284.7	286.7	1.29	12900	1.72	10.2	3100	2400	230	19	1	13	12.1	20.0	37	0.22
KL40-03	286.7	288.7	2.05	20500	1.24	9	239	810	110	67	1	14	8.5	21.0	68	0.18
KL40-03	288.7	290.7	1.27	12700	0.69	7.8	335	550	100	372	12	16	5.3	61.0	60	0.1
KL40-03	290.7	293.7	0.95	9500	0.65	10.7	1870	910	110	630	42	12	2.7	115.0	71	0.01
KL40-03	293.7	295.7	1.75	17500	0.88	7.3	2520	6500	660	24	7	19	6.6	12.0	27	0.01
KL40-03	295.7	297.7	0.92	9200	0.74	5.9	2150	1700	540	28	7	14	2.2	11.0	128	0.1
KL40-03	297.7	299.7	0.62	6200	0.62	3.8	246	99	220	247	23	41	2.7	18.5	38	0.01
KL40-03	299.7	302.7	0.481	4810	0.84	3.4	1800	362	1280	780	11	30	2.5	11.3	55	0.01
KL40-03	302.7	305.7	1.99	19900	1.48	10.5	2190	287	160	98	4	30	2.2	14.8	84	0.01
KL40-03	305.7	308.7	1.78	17800	1.78	23.8	1310	256	54	44	5	16	1.5	13.0	28	0.01
KL40-03	308.7	311.7	1.36	13600	1.4	14.5	410	83	58	53	11	24	1.7	22.5	101	0.01
KL40-03	311.7	314.7	1.44	14400	1.2	11.3	7060	43	66	6	34	31	1.3	13.0	28	0.01
KL40-03	314.7	317.7	0.92	9200	0.8	9.8	4080	72	100	144	34	25	2.6	12.8	34	0.01
KL40-03	317.7	320.7	2.23	22300	1.64	10.8	1630	43	410	270	34	32	1.8	11.0	64	0.1
KL40-03	320.7	323.7	5.06	50600	2.72	9.9	610	193	11	286	1	54	0.8	13.0	45	0.1
KL40-03	323.7	326.7	4.61	46100	2.05	14.7	430	295	6750	2400	4	46	4.2	16.0	79	0.2
KL40-03	326.7	329.7	2.49	24900	1.39	9.6	540	343	520	470	9	40	2	18.5	37	0.28
KL40-03	329.7	332.7	0.67	6700	1.68	21.5	2100	800	1230	6	91	21	6.1	51.3	49	0.85
KL40-03	332.7	335.7	1.66	16600	1.53	10.5	490	2800	370	7	32	18	4	12.5	52	0.68
KL40-03	335.7	338.2	4.24	42400	2.34	8.4	287	580	41	24	4	42	1.7	12.5	38	0.18
KL40-03	338.2	341.2	1.49	14900	0.8	4	196	71	28	13	4	36	1.2	15.5	24	0.16
KL40-03	341.2	344.3	3.91	39100	1.89	4.9	112	27	16	955	1	48	0.2	14.0	31	0.1
KL40-03	344.3	347.4	4.12	41200	1.32	5.6	102	36	8	1050	0.01	45	0.9	12.0	28	0.18
KL40-03	347.4	350.5	3.23	32300	1.94	8.5	223	73	20	28	4	59	0.9	14.0	32	0.1
KL40-03	350.5	353.6	2.31	23100	3.05	5.7	480	580	80	152	6	32	1.4	22.8	28	0.42
KL40-03	353.6	356.7	2.05	20500	1.83	3.6	196	192	32	131	3	41	0.8	15.0	27	0.15
KL40-03	356.7	359.7	2.51	25100	2.41	4.6	152	34	16	420	2	19	1	12.0	50	0.1
KL40-03	359.7	362.7	1.67	16700	1.75	4.5	84	41	23	69	9	51	0.8	19.0	36	0.01
KL40-03	362.7	365.7	2.39	23900	1.97	8.4	67	48	20	57	4	48	0.6	14.0	27	0.01
KL40-03	365.7	368.7	3.55	35500	1.63	5.3	226	78	64	51	4	91	0.9	37.5	39	0.21

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL40-03	368.7	371.7	2.52	25200	1.74	10.5	103	46	38	61	6	79	2.2	10.0	30	0.1
KL40-03	371.7	374.7	5.34	53400	2.41	15	1340	38	70	15	2	102	1.1	15.0	64	0.01
KL40-03	374.7	376.2	4.47	44700	1.36	11.2	175	64	69	31	4	62	1.5	24.0	96	0.16
KL40-03	376.2	380.7	1.76	17600	0.24	1.8	770	275	29	995	1	24	0.6	18.5	40	0.36
KL40-03	380.7	383.7	2.75	27500	0.27	2.2	58	380	86	130	2	33	1	33.0	57	0.1
KL40-03	383.7	386.7	1.27	12700	0.23	1.2	219	66	29	1570	3	16	0.5	27.0	152	0.18
KL40-03	386.7	389.7	0.65	6500	0.16	0.6	175	51	15	337	1	9	0.2	17.5	185	0.14
KL40-03	389.7	392.7	0.74	7400	0.2	0.7	820	302	19	234	1	25	0.4	25.0	55	0.18
KL40-03	392.7	395.7	1.35	13500	0.32	6.4	235	192	56	335	5	18	0.4	18.0	162	0.32
KL40-03	395.7	398.7	1.65	16500	0.41	8.8	76	159	60	203	1	12	0.2	15.5	73	0.36
KL40-03	398.7	401.7	1.24	12400	0.16	0.8	235	56	6	650	1	8	0.3	23.8	272	0.21
KL40-03	401.7	404.7	1.54	15400	0.15	1.2	34	32	10	470	2	13	0.3	21.0	266	0.17
KL40-03	404.7	407.7	1.47	14700	0.13	1	19	18	7	468	2	19	0.3	19.5	73	0.23
KL40-03	407.7	410.7	1.68	16800	0.13	1.5	42	40	12	500	3	15	0.4	29.0	172	0.24
KL40-03	410.7	413.7	1.58	15800	0.21	1.1	231	50	9	182	1	12	0.2	26.0	45	0.11
KL40-03	413.7	416.7	1.5	15000	0.26	1.2	126	110	33	195	1	20	0.5	30.5	172	0.22
KL40-03	416.7	419.7	2.2	22000	0.25	1.6	150	228	15	207	1	13	0.5	22.0	81	0.23
KL40-03	419.7	422.7	1.85	18500	0.25	1.7	248	77	14	770	1	13	0.2	33.0	78	0.24
KL40-03	422.7	425	2.01	20100	0.22	2.3	142	102	55	359	1	9	0.7	19.5	28	0.23
KL40-03	425	428.7	1.29	12900	0.13	1.5	90	45	12	290	1	17	0.01	24.5	63	0.2
KL40-03	428.7	431.7	0.92	9200	0.17	1.3	880	222	40	183	1	8	6.5	15.3	69	0.25
KL40-03	431.7	434.7	1.35	13500	0.14	2.3	640	292	46	150	2	13	2.6	24.0	146	0.21
KL40-03	434.7	437.7	0.96	9600	0.09	1.8	33	36	7	143	2	12	0.4	14.8	45	0.1
KL40-03	437.7	440.7	1.28	12800	0.12	3.8	56	26	6	302	6	19	0.01	23.5	50	0.15
KL40-03	440.7	443.7	0.65	6500	0.09	1.5	41	26	7	162	5	27	1.1	16.5	173	0.11
KL40-03	443.7	446.7	0.97	9700	0.11	4.6	730	141	12	87	5	13	0.8	13.8	78	0.21
KL40-03	446.7	449.7	0.74	7400	0.08	3.6	141	54	11	192	8	19	0.5	17.7	146	0.2
KL40-03	449.7	452.7	1.06	10600	0.14	6.8	301	83	10	189	15	20	0.5	16.8	66	0.26
KL40-03	452.7	455.7	1.02	10200	0.18	3.2	2370	2300	9	263	12	18	0.6	22.3	40	0.45
KL40-03	455.7	458	0.85	8500	0.12	3	2210	339	10	153	12	18	0.4	16.5	53	0.59
KL40-03	458	461.1	0.76	7600	0.11	1.6	141	116	34	68	8	21	0.7	15.0	70	0.2
KL40-03	461.1	464.2	0.82	8200	0.12	2.3	164	60	15	690	3	29	0.5	17.2	207	0.17
KL40-03	464.2	467.3	1.39	13900	0.1	4.6	82	117	16	365	6	11	0.4	16.0	64	0.22
KL40-03	467.3	470.4	0.94	9400	0.09	2.3	360	240	36	310	1	10	0.8	11.0	53	0.25
KL40-03	470.4	473.5	0.95	9500	0.14	1.2	55	56	13	259	1	10	0.7	16.5	50	0.13
KL40-03	473.5	476.6	0.95	9500	0.12	1	115	44	35	214	2	12	7.3	9.2	136	0.18
KL40-03	476.6	479.7	1.04	10400	0.06	2.8	400	233	22	110	4	9	0.6	14.0	44	0.39
KL40-03	479.7	482.7	0.284	2840	0.08	1.8	365	130	54	169	4	13	3	19.4	168	0.19
KL40-03	482.7	485.7	0.464	4640	0.13	1.1	176	54	35	390	4	22	0.8	21.2	61	0.12
KL40-03	485.7	488.7	1.94	19400	0.24	2.7	94	59	66	192	4	32	2.5	25.2	51	0.32
KL40-03	488.7	490.8	2.84	28400	0.32	3.6	148	46	40	50	4	13	1.6	20.0	70	0.16
KL40-03	490.8	492.8	1.15	11500	0.35	2.7	157	68	80	500	7	47	2	20.5	38	0.16
KL40-03	492.8	495.1	0.63	6300	0.17	2.1	76	140	320	260	13	13	19.4	26.8	82	0.12
KL40-03	495.1	497.7	0.87	8700	0.18	10.8	130	62	420	394	5	7	132	12.9	103	0.7
KL40-03	497.7	500.7	0.58	5800	0.1	1.9	113	314	48	540	7	23	1.5	18.0	107	0.14
KL40-03	500.7	503.7	0.353	3530	0.09	1.6	255	304	180	361	3	6	8.5	10.0	123	0.15
KL40-03	503.7	506.7	0.343	3430	0.05	1.8	500	196	87	216	2	7	3.5	12.1	141	0.18
KL40-03	506.7	509.7	0.74	7400	0.2	2.8	57	39	190	271	4	10	29	14.9	142	0.13
KL40-03	509.7	512.7	0.5	5000	0.52	1.5	20	25	28	48	2	8	1.8	5.5	81	0.01
KL40-03	512.7	515.7	0.64	6400	0.12	1.7	62	77	58	246	2	14	6.3	7.3	78	0.1
KL40-03	515.7	518.7	2.08	20800	0.63	65	168	9	2420	1260	34	8	1210	4.2	50	2.9
KL40-03	518.7	521.7	0.49	4900	0.23	8.2	88	119	1170	136	9	10	166	11.7	180	0.62
KL40-03	521.7	524.4	1.41	14100	0.59	30.1	114	20	2020	92	12	7	196	4.9	97	0.66
KL40-03	524.4	527.7	2.02	20200	1.22	53	254	8	2250	394	27	7	415	7.0	90	1.12
KL40-03	527.7	530.7	1.26	12600	0.55	22.5	166	17	1950	247	14	10	426	9.0	91	1.02
KL40-03	530.7	533.7	1.32	13200	0.86	34	163	251	2470	450	26	10	350	7.0	168	0.86
KL40-03	533.7	536.3	1.89	18900	1.23	44	32	31	2720	182	29	11	510	7.4	81	1.36
KL40-03	536.3	540.7	1.38	13800	0.97	36.5	72	29	1680	180	31	6	340	8.5	85	1.22
KL40-03	540.7	542.7	0.32	3200	0.4	25.8	55	129	760	102	12	6	182	6.5	64	0.57
KL40-03	542.7	545.7	0.4	4000	0.47	24.7	56	130	700	100	16	7	120	15.4	154	0.44
KL40-03	545.7	548.7	0.48	4800	0.29	6.7	35	127	400	46	12	13	30	8.3	188	0.7
KL40-03	548.7	551.7	0.67	6700	0.41	23.2	50	139	950	98	15	17	78	9.8	206	0.76
KL40-03	551.7	554.7	0.44	4400	0.2	15.6	66	165	280	68	18	8	19.9	9.0	140	0.36

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL40-03	743.7	746.9															
KL40-03	746.9	749.7															
KL40-03	749.7	752.7															
KL40-03	752.7	755.7															
KL40-03	755.7	758.7															
KL40-03	758.7	761.7															
KL40-03	761.7	764.7															
KL40-03	764.7	767.7															
KL40-03	767.7	770.7															
KL40-03	770.7	773.7															
KL40-03	773.7	776.7															
KL40-03	776.7	779.7															
KL40-03	779.7	782.7															
KL40-03	782.7	785.7															
KL40-03	785.7	788.7															
KL40-03	788.7	791.7															
KL40-03	791.7	794.7															
KL40-03	794.7	797.7															
KL40-03	797.7	800.7															
KL40-03	800.7	803.7															
KL40-03	803.7	806.7															
KL40-03	806.7	809.7															
KL40-03	809.7	812.7															
KL40-03	812.7	815.7															
KL40-03	815.7	818.7															
KL40-03	818.7	821.7															
KL40-03	821.7	824.7															
KL40-03	824.7	827.7															
KL40-03	827.7	830.6															
KL40-03	830.6	833.6															
KL40-03	833.6	836.7															
KL40-03	836.7	839.7															
KL40-03	839.7	842.6															
KL40-03	842.6	845.6															
KL40-03	845.6	848.6															
KL40-03	848.6	851.6															
KL40-03	851.6	854.6															
KL40-03	854.6	857.7															
KL40-03	857.7	875.7															
KL40-03	875.7	878.7															
KL40-03	878.7	881.7															
KL40-03	881.7	884.7															
KL40-03	884.7	887.7															
KL40-03	887.7	890.7															
KL40-03	890.7	893.7															
KL40-03	893.7	896.7															
KL40-03	896.7	899.7															
KL40-03	899.7	902.4															
KL40-03	902.4	905.4															
KL40-03	905.4	908.6															
KL40-03	908.6	911.7															
KL40-03	911.7	914.7															
KL40-03	914.7	917.7															
KL40-03	917.7	920.6															
KL40-03	920.6	923.6															
KL40-03	923.7	926.7															
KL40-03	926.7	929.7															
KL40-03	929.7	932.5															
KL40-04	0	3.2	0.0041		41	0.01	0.1	181	115	7	5	0.01	1	1.9	1.4	14	0.01
KL40-04	3.2	5.5	0.0059		59	0.01	0.1	206	92	7	3	0.01	1	1.3	1.2	13	0.01
KL40-04	5.5	9.8	0.0065		65	0.04	0.8	316	114	10	8	1	1	2.9	1.6	14	0.1
KL40-04	9.8	13.2	0.0037		37	0.04	0.8	428	256	16	5	0.01	1	6	2.2	16	0.13
KL40-04	13.2	15.6	0.0091		91	0.05	2.8	1010	830	50	4	1	1	20.4	5.4	15	0.36

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL40-04	15.6	18.7	0.0025		25	0.06	0.6	550	191	16	4	0.01	1	6.1	1.3	15	0.43
KL40-04	18.7	21.8	0.0021		21	0.03	0.1	372	210	15	4	0.01	1	3.2	1.2	14	0.11
KL40-04	21.8	24.7	0.0082		82	0.06	1.3	870	1370	23	12	0.01	1	7.8	4.7	22	0.25
KL40-04	24.7	27.9	0.0023		23	0.06	0.7	540	440	18	6	0.01	1	5.3	2.0	17	0.3
KL40-04	27.9	31	0.0033		33	0.02	0.1	332	229	6	3	1	1	2.3	1.2	13	0.01
KL40-04	31	34.3	0.0161		161	0.1	1.5	1110	800	25	27	16	1	8.9	7.5	19	0.19
KL40-04	34.3	37.5	0.0026		26	0.01	0.1	250	121	100	7	1	10	8.1	1.8	8	0.01
KL40-04	37.5	40.2	0.0057		57	0.16	1.5	2170	1420	43	16	1	1	13.7	7.2	17	0.36
KL40-04	40.2	42.5	0.0074		74	0.05	1.2	1630	1160	48	17	10	2	15.7	2.8	12	0.17
KL40-04	42.5	44.5	0.0225		225	0.01	0.1	331	354	54	6	3	11	4.4	3.0	31	0.01
KL40-04	44.5	47.3	0.0225		225	0.03	0.8	240	243	51	7	5	22	5.8	6.2	29	0.01
KL40-04	47.3	51.4	0.0026		26	0.1	0.7	1100	630	24	7	1	1	7.4	4.7	17	0.29
KL40-04	51.4	54.4	0.0131		131	0.01	0.1	600	182	47	79	10	3	9	1.4	22	0.01
KL40-04	54.4	56.5	0.0332		332	0.03	1.6	940	590	130	33	56	4	25	3.1	23	0.01
KL40-04	56.5	59.5	0.0123		123	0.05	0.8	880	315	75	18	7	2	9.5	3.0	29	0.17
KL40-04	59.5	62.1	0.0139		139	0.01	0.1	470	133	54	12	26	1	5.2	2.5	15	0.01
KL40-04	62.1	65.5	0.0068		68	0.1	0.6	840	342	18	9	2	1	5.3	1.8	14	0.1
KL40-04	65.5	68.5	0.0053		53	0.22	0.1	490	217	36	15	4	1	14.4	1.4	15	0.19
KL40-04	68.5	71.5	0.0067		67	0.07	0.6	480	165	26	18	4	1	5.9	0.8	18	0.1
KL40-04	71.5	74.5	0.0059		59	0.03	1.1	770	352	67	75	7	1	14.1	1.6	37	0.18
KL40-04	74.5	77.5	0.0182		182	0.03	2	460	329	37	16	45	1	5.7	2.3	32	0.01
KL40-04	77.5	80.5	0.0093		93	0.01	2.6	203	230	43	81	72	1	2.9	3.4	19	0.14
KL40-04	80.5	83.5	0.0064		64	0.02	1.6	153	208	33	79	48	1	1.9	2.4	25	0.01
KL40-04	83.5	86.5	0.0082		82	0.02	5	200	396	27	13	45	1	4.7	2.8	19	0.01
KL40-04	86.5	89.1	0.0073		73	0.03	1	880	304	39	8	23	1	9.8	3.7	40	0.12
KL40-04	89.1	92.2	0.0046		46	0.02	0.6	500	192	22	11	3	1	6	1.5	35	0.01
KL40-04	92.2	95.2	0.0118		118	0.03	0.8	241	190	24	108	22	2	2.5	1.6	26	0.01
KL40-04	95.2	98.3	0.0304		304	0.15	2.1	1270	540	79	167	24	1	16.3	5.8	32	0.16
KL40-04	98.3	101.4	0.0099		99	0.13	1.8	1870	770	130	28	14	1	28	6.5	32	0.18
KL40-04	101.4	104.5	0.01		100	0.12	4.3	2300	1110	65	23	4	1	18	6.0	18	0.12
KL40-04	104.5	107.5	0.0134		134	0.06	3.7	3450	1900	35	7	1	1	24	6.5	18	0.17
KL40-04	107.5	110.5	0.0209		209	0.06	2.3	2540	730	50	9	4	3	12.4	3.8	22	0.01
KL40-04	110.5	114	0.0394		394	0.08	28	12600	8100	110	32	120	2	24	84.8	24	0.01
KL40-04	114	116.3	0.0037		37	0.04	1	470	400	24	6	2	1	3.3	4.4	25	0.01
KL40-04	116.3	119.3	0.0021		21	0.02	0.8	311	450	33	4	2	3	2.7	1.4	26	0.01
KL40-04	119.3	122.4	0.006		60	0.08	1.2	530	500	57	7	4	1	3.2	1.8	29	0.01
KL40-04	122.4	125.5	0.0146		146	0.08	0.8	257	372	34	12	1	2	2.5	2.1	44	0.01
KL40-04	125.5	128.5	0.0016		16	0.16	0.7	260	277	39	3	1	1	4.3	3.6	25	0.01
KL40-04	128.5	131.5	0.47		4700	0.28	106	42900	110800	970	7	90	3	90	33.0	35	0.93
KL40-04	131.5	134.5	0.0192		192	0.08	6.6	315	600	26	7	186	5	2.9	23.9	19	0.01
KL40-04	134.5	137.5	0.0074		74	0.02	1.2	450	780	27	4	2	1	2.3	3.3	23	0.01
KL40-04	137.5	140.5	0.004		40	0.04	1.2	232	430	67	3	4	1	3.3	5.0	26	0.01
KL40-04	140.5	143.5	0.0262		262	0.06	1.4	1230	650	70	5	5	1	10	5.4	22	0.01
KL40-04	143.5	146.5	0.056		560	0.05	6.6	1930	470	48	8	25	3	4.2	16.0	25	0.01
KL40-04	146.5	149.5	0.0042		42	0.05	0.7	125	111	36	3	3	1	1.3	2.6	17	0.01
KL40-04	149.5	152.5	0.0134		134	0.16	10.4	4090	1630	95	2	46	3	5.6	21.3	27	0.12
KL40-04	152.5	155.5	0.014		140	0.18	1.5	480	126	67	5	14	1	6.8	8.5	24	0.01
KL40-04	155.5	158.5	0.0043		43	0.07	0.5	146	124	38	6	4	1	2.6	3.2	33	0.01
KL40-04	158.5	161.5	0.074		740	0.48	1.7	2000	950	54	1500	7	5	5.3	7.8	107	0.01
KL40-04	161.5	164.5	0.0072		72	0.11	1	256	123	47	11	16	3	2.9	7.9	37	0.01
KL40-04	164.5	167.5	0.0017		17	0.02	0.1	185	148	14	4	1	1	0.9	3.1	19	0.01
KL40-04	167.5	170.5	0.008		80	0.02	0.1	140	72	10	12	2	1	0.9	1.2	21	0.01
KL40-04	170.5	173.5	0.0101		101	0.12	0.1	115	224	42	3	1	1	2.4	3.0	36	0.01
KL40-04	173.5	176.5	0.0086		86	0.11	3.2	1990	1060	58	5	24	2	4	13.8	36	0.01
KL40-04	176.5	179.5	0.0068		68	0.07	0.6	500	540	37	9	7	1	1.6	6.7	33	0.01
KL40-04	179.5	182.5	0.06		600	0.22	0.7	1360	382	160	4	12	5	16.1	24.7	58	0.01
KL40-04	182.5	185.5	0.0201		201	0.09	0.9	2030	510	64	112	4	4	12.1	6.8	135	0.1
KL40-04	185.5	188.5	0.0083		83	0.05	0.1	137	72	24	12	4	4	2.4	3.9	101	0.01
KL40-04	188.5	191.5	0.0182		182	0.05	0.1	169	67	27	98	2	2	3.1	2.4	122	0.01
KL40-04	191.5	194.5	0.0215		215	0.05	0.1	171	81	26	12	1	1	2.4	2.3	72	0.01
KL40-04	194.5	197.5	0.0217		217	0.04	0.1	145	94	11	15	0.01	1	1.3	2.2	60	0.01
KL40-04	197.5	200.5	0.0394		394	0.09	1.3	490	400	21	36	4	2	8	1.3	123	0.01
KL40-04	200.5	203.5	1.27		12700	0.75	5.4	780	295	4500	38	7	14	145	25.0	160	0.18

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL40-04	203.5	206.5	0.72	7200	0.44	5	287	317	2250	332	14	19	80	20.0	103	0.01
KL40-04	206.5	209.5	0.142	1420	0.27	1.7	386	138	560	296	2	5	22	4.5	270	0.01
KL40-04	209.5	212.5	0.67	6700	0.54	1.8	1050	117	2500	830	2	4	65	4.4	215	0.01
KL40-04	212.5	215.5	0.343	3430	0.62	1.2	133	75	1180	2050	3	7	35	6.5	243	0.01
KL40-04	215.5	218.5	0.505	5050	0.52	1	268	77	1690	1320	2	3	55	6.0	176	0.1
KL40-04	218.5	221.5	0.59	5900	0.4	2.8	760	175	2030	805	6	4	65	10.8	195	0.1
KL40-04	221.5	224.5	0.523	5230	0.18	3	88	72	1710	892	2	6	65	11.0	103	0.01
KL40-04	224.5	227.5	0.162	1620	0.28	1.3	161	47	380	739	2	24	21.6	19.0	160	0.01
KL40-04	227.5	230.5	0.192	1920	0.34	2.6	850	141	280	1500	2	9	26	7.2	115	0.12
KL40-04	230.5	233.1	0.119	1190	0.26	2.5	640	91	69	850	2	3	8.7	6.0	98	0.01
KL40-04	233.1	236.2	0.085	850	0.17	1.4	690	118	80	16	3	1	1.7	7.8	16	0.01
KL40-04	236.2	239.5	0.141	1410	0.42	2.7	1330	680	98	1550	3	5	4.8	7.9	178	0.11
KL40-04	239.5	242.5	0.08	800	0.16	2.4	1420	690	51	529	2	3	3.8	6.6	105	0.01
KL40-04	242.5	245.5	0.164	1640	0.27	4.4	2870	1530	120	492	4	6	6.5	25.0	150	0.1
KL40-04	245.5	248.5	0.114	1140	0.32	3.7	2470	970	100	470	2	5	5.5	16.8	148	0.11
KL40-04	248.5	251.5	0.041	410	0.16	1.5	430	382	31	386	1	5	3.8	8.9	76	0.01
KL40-04	251.5	254.5	0.082	820	0.24	2.3	860	372	90	124	2	6	4.1	12.9	123	0.01
KL40-04	254.5	257.5	0.119	1190	0.64	6.1	10200	2600	230	738	4	8	23.1	23.0	108	0.34
KL40-04	257.5	260.5	0.077	770	0.11	14.5	367	341	130	305	35	3	4	12.5	25	0.01
KL40-04	260.5	262.5	3.7	37000	1.87	17.4	15400	7000	450	423	290	42	400	40.0	117	1.44
KL40-04	262.5	266.5	0.63	6300	1	11.3	11400	1160	100	500	256	34	15.1	27.3	26	0.6
KL40-04	266.5	269.5	0.139	1390	0.36	8.9	710	420	61	312	38	6	4.3	7.0	25	0.01
KL40-04	269.5	272.5	0.0287	287	0.19	9.2	480	400	36	330	70	2	2.2	6.5	21	0.01
KL40-04	272.5	275.5	0.0382	382	0.55	4.7	3400	950	64	385	16	4	6.4	8.9	25	0.12
KL40-04	275.5	278.5	0.0123	123	0.04	2.1	87	156	31	38	14	1	1.7	5.3	19	0.01
KL40-04	278.5	281.5	0.0319	319	0.21	4.5	1290	389	42	157	13	2	3.4	7.8	23	0.01
KL40-04	281.5	284.3	0.041	410	0.18	11.6	1060	1000	48	320	40	3	6.6	13.1	20	0.01
KL40-04	284.3	287.5	0.0307	307	0.29	8.8	1830	2600	100	200	32	1	4.8	11.6	22	0.14
KL40-04	287.5	290.3	0.0183	183	0.06	3.3	201	186	43	245	19	1	2	7.2	32	0.01
KL40-04	290.3	293.4	0.089	890	0.1	10.4	570	409	37	299	38	4	0.9	11.7	32	0.01
KL40-04	293.4	296.3	0.123	1230	0.18	21.9	560	490	88	217	56	11	2.4	13.5	30	0.01
KL40-04	296.3	299.5	0.0118	118	0.12	3.7	211	295	44	64	25	1	1.8	5.8	32	0.01
KL40-04	299.5	302.5	0.0101	101	0.06	3.9	137	243	31	40	21	1	1.3	4.0	28	0.01
KL40-04	302.5	305.7	0.0147	147	0.07	5.1	610	520	42	39	30	1	3	9.1	25	0.01
KL40-04	305.7	308.4	0.0072	72	0.07	2.2	470	480	29	27	9	1	1.3	5.5	20	0.01
KL40-04	308.4	311.3	0.0115	115	0.03	0.7	197	157	9	22	3	1	0.6	2.9	11	0.01
KL40-04	311.3	314.5	0.09	900	0.15	0.9	520	348	22	22	3	1	1.5	7.4	14	0.01
KL40-04	314.5	317.5	0.0131	131	0.02	0.1	243	130	10	11	1	1	0.6	2.8	10	0.01
KL40-04	317.5	320.5	0.158	1580	0.06	1.8	1380	880	51	8	3	1	10.9	9.6	12	0.01
KL40-04	320.5	323.5	0.0154	154	0.03	1	287	750	19	6	2	1	0.8	8.8	12	0.01
KL40-04	323.5	326.5	0.0034	34	0.02	0.8	184	600	10	7	2	1	0.7	10.9	16	0.01
KL40-04	326.5	329.9	0.0229	229	0.06	3.9	1570	1860	26	10	22	1	2.2	13.9	20	0.01
KL40-04	329.9	332.5	0.0175	175	0.05	2	880	356	30	82	8	1	1.6	12.2	19	0.01
KL40-04	332.5	335.5	0.065	650	0.07	2.3	870	312	42	12	10	1	2.9	12.7	13	0.01
KL40-04	335.5	338.5	0.06	600	0.06	5.4	570	610	55	44	12	1	5.6	12.0	13	0.01
KL40-04	338.5	341.5	0.084	840	0.08	3	1140	570	100	16	4	1	6.8	10.0	18	0.01
KL40-04	341.5	344.2	0.0346	346	0.06	1.1	262	120	54	12	2	1	1.2	6.3	15	0.01
KL40-04	344.2	347.3	0.184	1840	0.59	7.6	5900	1380	140	2030	7	5	5.8	13.0	161	0.3
KL40-04	347.3	352.1	0.144	1440	0.29	1.9	1320	318	98	24	4	1	1.2	17.4	16	0.01
KL40-04	352.1	356.5	0.091	910	0.18	3.5	760	289	140	12	44	1	1.6	12.6	8	0.01
KL40-04	356.5	359.5	0.175	1750	0.36	3.4	750	236	37	17	58	4	1.4	12.5	16	0.01
KL40-04	359.5	362.6	0.25	2500	0.31	1.6	690	70	44	5	5	3	1.1	8.2	20	0.01
KL40-04	362.6	365.5	0.378	3780	0.29	1.4	510	50	31	4	3	14	2.6	6.3	22	0.01
KL40-04	365.5	368.5	0.415	4150	0.4	1.2	340	30	48	11	2	11	2.6	6.9	22	0.01
KL40-04	368.5	371.5	1	10000	1.29	3.8	314	25	39	8	2	19	1.7	15.6	20	0.01
KL40-04	371.5	374.5	1.04	10400	0.35	1.4	128	26	25	91	74	14	11	17.4	29	0.01
KL40-04	374.5	377.5	0.407	4070	0.17	0.8	152	24	27	700	6	17	3.7	3.0	27	0.01
KL40-04	377.5	380.5	1.42	14200	0.52	1.5	251	143	3	93	3	16	1.8	8.0	36	0.01
KL40-04	380.5	382.7	0.154	1540	0.15	0.8	232	158	54	27	0.01	7	1.3	4.8	24	0.01
KL40-04	382.7	385.4	0.18	1800	0.11	0.7	158	37	42	20	0.01	5	0.8	2.8	18	0.01
KL40-04	385.4	388.2	0.141	1410	0.11	0.9	143	36	33	100	3	5	2	7.5	35	0.01
KL40-04	388.2	392.5	0.23	2300	0.15	0.9	81	24	16	107	1	8	1.2	8.7	30	0.01
KL40-04	392.5	395.5	0.27	2700	0.08	0.8	59	17	17	39	0.01	6	1.6	4.6	16	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL40-04	395.5	398.5	0.23	2300	0.21	0.7	244	37	23	19	0.01	7	2.1	4.1	28	0.01
KL40-04	398.5	401	0.075	750	0.06	0.6	160	18	19	21	0.01	6	0.9	1.4	30	0.01
KL40-04	401	404.5	0.38	3800	0.14	0.8	200	33	4	104	1	11	0.4	3.9	22	0.01
KL40-04	404.5	407.5	0.55	5500	0.27	3.5	4160	600	39	127	2	16	3.4	7.2	40	0.01
KL40-04	407.5	410.5	0.416	4160	0.15	4.6	1650	3610	59	75	4	9	5.2	4.0	31	0.01
KL40-04	410.5	413.2	0.69	6900	0.29	1.5	76	31	11	103	1	12	1.1	5.2	10	0.01
KL40-04	413.2	416.5	0.3	3000	0.15	0.7	98	28	11	43	0.01	11	0.5	3.2	18	0.01
KL40-04	416.5	419.5	0.468	4680	0.14	0.8	1580	16	36	56	5	21	2.2	6.6	20	0.01
KL40-04	419.5	422.2	1.81	18100	0.53	2	2380	11	4	13	1	51	1.1	18.5	16	0.01
KL40-04	422.2	425.3	0.403	4030	0.3	1.2	186	14	19	20	0.01	24	0.6	4.6	21	0.01
KL40-04	425.3	428.6	0.32	3200	0.15	0.8	88	34	10	24	0.01	11	0.4	3.9	14	0.01
KL40-04	428.6	431.6	0.74	7400	0.38	1.5	440	34	16	18	3	22	1	5.0	20	0.01
KL40-04	431.6	434.5	0.68	6800	0.36	1.3	850	49	25	63	0.01	29	1.8	9.4	24	0.01
KL40-04	434.5	437.1	0.57	5700	0.2	1	167	13	11	56	0.01	21	2	2.0	17	0.01
KL40-04	437.1	440.5	0.93	9300	0.32	2	1850	28	16	10	3	25	1.5	5.4	23	0.01
KL40-04	440.5	442.5	0.68	6800	0.34	1.8	347	18	25	5	11	16	2.2	3.6	18	0.01
KL40-04	442.5	445.1	0.61	6100	0.51	2.7	1290	355	34	5	1	9	2.1	3.0	17	0.01
KL40-04	445.1	448	0.115	1150	0.12	0.9	1100	326	23	3	0.01	5	1.3	0.8	11	0.01
KL40-04	448	450.9	0.22	2200	0.15	0.7	640	58	21	4	0.01	6	1	2.6	10	0.01
KL40-04	450.9	452.3	0.54	5400	0.35	1.7	760	166	50	3	3	14	5.7	12.2	22	0.01
KL40-04	452.3	455.4	0.91	9100	0.95	2.4	1970	239	44	7	5	25	7.8	13.5	50	0.01
KL40-04	455.4	459.1	0.79	7900	1.04	1.3	450	80	12	4	4	35	1.3	7.8	36	0.01
KL40-04	459.1	461.5	0.32	3200	0.26	1.3	1010	490	9	21	2	7	1.2	5.5	19	0.01
KL40-04	461.5	463.7	0.33	3300	0.29	3.8	1170	1210	19	26	7	7	2.2	3.4	21	0.01
KL40-04	463.7	466.8	0.172	1720	0.43	1.1	159	63	21	43	0.01	7	1.4	3.1	8	0.01
KL40-04	466.8	470	0.348	3480	0.28	1	225	259	15	114	0.01	10	0.7	2.5	12	0.01
KL40-04	470	473.1	0.421	4210	0.39	1	420	630	17	17	0.01	7	0.7	2.9	21	0.01
KL40-04	473.1	476.2	0.22	2200	0.24	0.8	160	108	14	21	1	7	0.6	2.7	38	0.01
KL40-04	476.2	478.9	0.18	1800	0.14	0.1	167	379	11	6	0.01	5	0.7	2.6	39	0.01
KL40-04	478.9	482.1	0.173	1730	0.15	0.9	1850	1810	8	24	1	6	1.1	3.4	74	0.01
KL40-04	482.1	485.2	0.29	2900	0.26	0.8	178	98	7	9	1	7	1	3.0	76	0.01
KL40-04	485.2	488.3	0.23	2300	0.23	0.6	113	56	7	8	1	7	0.6	2.8	76	0.01
KL40-04	488.3	491.4	0.43	4300	0.18	1	181	298	7	18	0.01	6	0.7	4.2	70	0.01
KL40-04	491.4	494.5	0.385	3850	0.2	1.2	302	221	7	13	1	8	1.6	4.6	61	0.01
KL40-04	494.5	497	0.544	5440	0.1	3.2	128	46	180	8	27	5	120	24.0	66	0.01
KL40-04	497	500.5	0.19	1900	0.13	1.8	131	106	18	85	8	14	9.3	23.9	83	0.01
KL40-04	500.5	503.4	0.154	1540	0.18	2	32	21	4	14	7	5	1.3	2.7	61	0.01
KL40-04	503.4	506.5	0.096	960	0.1	1.2	67	123	5	12	2	5	0.6	2.1	57	0.01
KL40-04	506.5	509.2	0.086	860	0.07	0.9	283	228	4	15	1	4	0.7	1.3	70	0.01
KL40-04	509.2	512.2	0.058	580	0.04	0.8	34	30	2	25	2	6	0.6	1.8	86	0.01
KL40-04	512.2	515.6	0.23	2300	0.15	1.4	66	51	8	41	7	5	2.6	3.9	57	0.01
KL40-04	515.6	518.5	0.07	700	0.03	0.6	126	216	5	27	0.01	5	0.8	0.7	112	0.01
KL40-04	518.5	521.5	0.075	750	0.04	0.1	71	38	2	16	0.01	6	0.3	2.0	97	0.01
KL40-04	521.5	524.5	0.112	1120	0.08	0.6	57	34	3	131	0.01	5	0.6	1.1	93	0.01
KL40-04	524.5	527.5	0.179	1790	0.06	1.3	25	19	3	600	7	3	1	2.5	108	0.01
KL40-04	527.5	530.3	0.083	830	0.03	1	40	21	2	39	1	6	0.5	1.1	79	0.01
KL40-04	530.3	533.4	0.115	1150	0.03	0.9	45	29	1	92	2	4	0.01	1.4	129	0.01
KL40-04	533.4	536.5	0.097	970	0.04	1	88	76	1	296	5	5	0.5	1.2	94	0.01
KL40-04	536.5	539	0.141	1410	0.08	1.4	104	54	2	330	3	3	2.3	1.8	112	0.01
KL40-04	539	543.6	0.104	1040	0.11	0.7	72	49	37	186	5	13	9.8	12.4	101	0.01
KL40-04	543.6	547.7	0.139	1390	0.07	1	85	50	21	144	5	6	7.2	6.1	121	0.01
KL40-04	547.7	550.8	0.199	1990	0.04	1.8	43	27	4	150	4	7	1.5	3.0	87	0.01
KL40-04	550.8	554	0.175	1750	0.09	1.1	59	44	4	16	2	4	0.8	1.9	132	0.01
KL40-04	554	556.7	0.406	4060	0.15	1.5	71	55	15	23	4	4	2.6	1.4	129	0.01
KL40-04	556.7	560.3	0.134	1340	0.05	0.1	13	24	64	181	1	5	7.8	1.3	189	0.01
KL40-04	560.3	563.6	0.045	450	0.08	0.1	24	20	20	81	1	3	3	1.6	134	0.01
KL40-04	563.6	566.5	0.061	610	0.08	0.1	35	29	56	57	1	3	5.1	1.5	176	0.01
KL40-04	566.5	569.5	0.043	430	0.04	0.1	17	13	93	46	0.01	8	6.3	1.7	174	0.01
KL40-04	569.5	572.5	0.103	1030	0.1	0.1	24	23	89	42	1	1	6.5	1.7	93	0.01
KL40-04	572.5	575.5	0.405	4050	0.11	0.1	29	18	150	18	1	2	25	1.4	180	0.01
KL40-04	575.5	578.5	0.19	1900	0.11	0.1	48	46	180	62	1	2	40	2.2	100	0.01
KL40-04	578.5	581.5	0.247	2470	0.07	0.1	65	24	320	39	1	2	32	1.8	103	0.01
KL40-04	581.5	584.5	0.11	1100	0.04	0.1	37	22	26	64	0.01	1	3.9	2.7	181	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL40-04	584.5	587.5	0.058		580	0.07	0.1	155	88	81	97	1	3	6	4.4	158	0.01
KL40-04	587.5	590.1	1.83	18300	1.03	14.2	3390	3010	5800	44	4	3	274	5.0	170	0.23	
KL40-04	590.1	593.1	0.133	1330	0.25	0.8	1050	440	270	54	1	3	21	3.6	72	0.01	
KL40-04	593.1	596	0.043	430	0.07	0.1	76	59	53	35	0.01	2	6	2.8	177	0.01	
KL40-04	596	599.5	0.0164	164	0.03	0.1	73	30	20	22	1	1	5.1	5.1	147	0.01	
KL40-04	599.5	602.8	0.014	140	0.02	0.1	34	14	13	53	0.01	1	2.3	7.0	87	0.01	
KL40-04	602.8	605.7	0.0365	365	0.02	0.1	21	8	5	1010	0.01	2	1.1	8.1	98	0.01	
KL40-04	605.7	609.6	0.0235	235	0.01	0.1	14	6	4	830	0.01	1	1	3.9	62	0.01	
KL40-04	609.6	613.5	0.0112	112	0.01	0.1	116	152	4	80	0.01	1	0.8	2.1	98	0.01	
KL40-04	613.5	617.5	0.0125	125	0.03	0.1	15	12	7	131	0.01	2	1.6	2.2	57	0.01	
KL40-04	617.5	620.5	0.0285	285	0.03	0.1	28	26	42	120	1	1	4.3	3.1	175	0.01	
KL40-04	620.5	623.5	0.0182	182	0.02	0.1	18	8	7	53	0.01	1	1	4.6	94	0.01	
KL40-04	623.5	626.5	0.0287	287	0.01	0.1	15	15	12	40	0.01	1	1.6	1.4	148	0.01	
KL40-04	626.5	629.5	0.061	610	0.03	0.1	23	12	100	40	0.01	3	19	2.2	78	0.01	
KL40-04	629.5	632.5	0.0305	305	0.03	0.1	22	10	16	49	0.01	1	19	2.0	151	0.01	
KL40-04	632.5	635.5	0.116	1160	0.03	0.9	69	22	220	41	1	1	3.5	1.9	64	0.01	
KL40-04	635.5	638.5	0.067	670	0.01	1	30	9	180	50	1	3	13.1	1.0	165	0.01	
KL40-04	638.5	641.5	0.089	890	0.01	0.7	15	6	160	47	0.01	1	6	1.4	85	0.01	
KL40-04	641.5	644.5	0.127	1270	0.03	0.1	17	19	300	160	1	1	8.9	1.6	89	0.01	
KL40-04	644.5	646.6	0.089	890	0.02	0.6	9	6	270	326	0.01	1	6.6	1.8	110	0.01	
KL40-04	646.6	649.1	0.0344	344	0.02	0.1	8	5	57	95	0.01	1	2.9	0.8	151	0.01	
KL40-04	649.1	653.5	0.0214	214	0.02	0.1	71	9	36	45	0.01	2	3.4	1.1	188	0.01	
KL40-04	653.5	656.5	0.0176	176	0.01	0.1	14	5	17	30	0.01	1	1.5	1.3	146	0.01	
KL40-04	656.5	659.5	0.0164	164	0.01	0.1	17	5	29	31	0.01	3	2.4	6.2	183	0.01	
KL40-04	659.5	662.5	0.0091	91	0.01	0.1	7	7	14	27	0.01	3	0.7	3.1	142	0.01	
KL40-04	662.5	665.5	0.0359	359	0.01	0.1	16	1	120	123	0.01	4	3.4	2.3	165	0.01	
KL40-04	665.5	668.5	0.062	620	0.03	0.1	229	16	150	39	1	3	8.7	2.5	124	0.01	
KL40-04	668.5	671.5	0.044	440	0.01	0.1	32	7	56	70	1	1	3.4	0.6	236	0.01	
KL40-04	671.5	674.5	0.0118	118	0.02	0.1	12	1	9	54	0.01	2	1.2	2.4	189	0.01	
KL40-04	674.5	677.5	0.0166	166	0.01	0.1	9	5	4	75	0.01	2	0.8	1.4	86	0.01	
KL40-04	677.5	680.5	0.0113	113	0.01	0.1	31	1	10	87	0.01	1	1	1.9	100	0.01	
KL40-04	680.5	683	0.0086	86	0.01	0.1	21	5	7	25	0.01	1	0.9	2.4	139	0.01	
KL40-04	683	686.1	0.0134	134	0.01	0.1	12	6	8	31	0.01	3	1.2	1.8	185	0.01	
KL40-04	686.1	689.2	0.0087	87	0.01	0.1	6	6	6	101	0.01	4	1	2.6	132	0.01	
KL40-04	689.2	692.3	0.0128	128	0.01	0.1	27	10	2	82	0.01	5	0.4	3.8	87	0.01	
KL40-04	692.3	695.4	0.0334	334	0.01	0.1	7	1	5	22	0.01	4	1.2	3.5	63	0.01	
KL40-04	695.4	698.6	0.0135	135	0.01	0.1	7	6	10	23	0.01	1	1.8	3.4	67	0.01	
KL40-04	698.6	701.5	0.0044	44	0.01	0.1	4	5	1	227	0.01	1	0.6	0.8	125	0.01	
KL40-04	701.5	704.5	0.007	70	0.01	0.1	8	7	0.01	270	0.01	1	0.9	1.5	175	0.01	
KL40-04	704.5	707.5	0.114	1140	0.01	0.1	40	14	0.01	61	0.01	1	0.6	0.8	118	0.01	
KL40-04	707.5	710.5	0.0104	104	0.01	0.1	13	7	10	40	0.01	1	1.4	3.4	118	0.01	
KL40-04	710.5	713.5	0.08	800	0.07	0.6	163	106	160	49	0.01	1	17.3	1.9	84	0.01	
KL40-04	713.5	716.5	0.0058	58	0.01	0.1	15	6	4	35	0.01	1	0.7	0.8	125	0.01	
KL40-04	716.5	719.3	0.047	470	0.01	0.1	14	6	3	52	1	1	1	2.3	100	0.01	
KL40-04	719.3	722.4	0.084	840	0.01	0.1	8	8	0.01	43	0.01	1	0.5	1.1	96	0.01	
KL40-04	722.4	725.5	0.041	410	0.01	0.1	4	6	33	29	0.01	1	3.8	0.7	106	0.01	
KL40-04	725.5	728.2	0.0256	256	0.01	0.1	5	7	15	32	0.01	1	2.4	1.5	134	0.01	
KL40-04	728.2	731.7	0.041	410	0.01	0.1	6	8	12	32	0.01	1	1.6	0.8	170	0.01	
KL40-04	731.7	734.6	0.0069	69	0.01	0.1	5	6	6	31	0.01	1	1.1	1.1	157	0.01	
KL40-04	734.6	737.4	0.0146	146	0.01	0.1	5	7	5	60	0.01	1	1.2	0.5	141	0.01	
KL40-04	737.4	740.5	0.0188	188	0.01	0.1	5	8	4	63	0.01	1	0.9	0.9	125	0.01	
KL40-04	740.5	743.5	0.0262	262	0.01	0.1	4	7	2	47	0.01	1	0.4	1.9	133	0.01	
KL40-04	743.5	746.5	0.0398	398	0.01	0.1	23	22	0.01	90	0.01	1	0.6	1.6	132	0.01	
KL40-04	746.5	749.5	0.0321	321	0.01	0.1	4	7	1	86	0.01	1	0.6	0.8	142	0.01	
KL40-04	749.5	752.5	0.0189	189	0.01	0.1	8	7	7	50	0.01	1	0.4	1.8	125	0.01	
KL40-04	752.5	755.5	0.069	690	0.01	0.1	9	8	8	40	0.01	1	2.1	1.7	63	0.01	
KL40-04	755.5	758.5	0.141	1410	0.03	0.1	55	17	4	70	0.01	1	0.6	1.5	130	0.01	
KL40-04	758.5	761.5	0.128	1280	0.01	0.1	44	21	5	66	0.01	1	0.6	1.0	125	0.01	
KL40-04	761.5	764.5	0.0322	322	0.01	0.1	11	9	5	58	0.01	1	1	1.7	135	0.01	
KL40-04	764.5	767.5	0.0327	327	0.01	0.1	8	12	1	150	0.01	1	0.4	1.9	123	0.01	
KL40-04	767.5	770.5	0.083	830	0.01	0.1	37	21	8	56	0.01	1	0.6	2.0	115	0.01	
KL40-04	770.5	773.5	0.136	1360	0.01	0.1	12	10	4	50	0.01	1	0.7	1.5	65	0.01	
KL40-04	773.5	776.5	0.045	450	0.01	0.1	19	16	4	72	0.01	1	0.7	2.0	96	0.01	

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL40-04	776.5	779.5	0.0104	104	0.01	0.1	4	8	18	100	0.01	1	0.8	3.2	55	0.01
KL40-04	779.5	782.5	0.0098	98	0.01	0.1	20	42	10	40	1	8	0.7	9.4	123	0.01
KL40-04	782.5	785.5	0.0089	89	0.01	0.1	22	41	13	297	1	6	0.6	4.9	124	0.01
KL40-04	785.5	788.5	0.0255	255	0.01	0.1	23	38	27	60	1	10	1.6	6.1	142	0.01
KL40-04	788.5	791.5	0.069	690	0.01	0.1	52	32	13	60	0.01	2	0.8	2.0	114	0.01
KL40-04	791.5	794.5	0.049	490	0.01	0.1	38	29	13	121	0.01	4	0.8	3.3	135	0.01
KL40-04	794.5	797.5	0.015	150	0.01	0.1	12	13	9	34	0.01	2	0.6	2.9	95	0.01
KL40-04	797.5	800.5	0.0257	257	0.01	0.1	42	24	0.01	80	0.01	1	0.4	2.7	123	0.01
KL40-04	800.5	803.5	0.023	230	0.01	0.1	17	13	1	61	0.01	3	0.4	2.4	124	0.01
KL40-04	803.5	806.5	0.0183	183	0.01	0.1	16	15	4	47	0.01	3	0.6	2.5	143	0.01
KL40-04	806.5	809.1	0.0174	174	0.01	0.1	11	10	2	60	0.01	3	0.3	2.3	123	0.01
KL40-05	0	4.5	0.0006	6	0.01	0.1	184	165	7	2	0.01	1	2.9	1.0	13	0.01
KL40-05	4.5	7.4	0.0006	6	0.02	0.1	212	118	6	4	0.01	1	4.4	1.4	16	0.01
KL40-05	7.4	10.3	0.005	50	0.05	3.2	890	580	18	2	2	1	16	6.3	14	0.01
KL40-05	10.3	13.7	0.0008	8	0.03	1	420	107	9	2	0.01	1	5.9	3.5	16	0.01
KL40-05	13.7	16.7	0.0016	16	0.14	1.2	920	429	23	3	0.01	1	9.5	14.3	20	0.01
KL40-05	16.7	19.7	0.0141	141	0.05	3	700	550	51	7	3	1	26	4.8	21	0.16
KL40-05	19.7	22.7	0.0012	12	0.05	0.9	460	377	20	3	0.01	1	4	2.5	22	0.01
KL40-05	22.7	25.5	0.0005	5	0.04	0.7	337	164	10	1	0.01	1	2.3	3.8	20	0.01
KL40-05	25.5	28.7	0.0024	24	0.05	1.4	1200	1550	30	1	0.01	3	13.3	2.0	20	0.13
KL40-05	28.7	31.7	0.0057	57	0.02	1	335	256	27	3	2	3	2.1	5.5	21	0.01
KL40-05	31.7	33.7	0.0039	39	0.01	0.6	132	120	8	1	1	2	1.2	1.5	19	0.01
KL40-05	33.7	36.7	0.002	20	0.01	0.6	206	183	10	5	1	1	2.8	1.3	16	0.01
KL40-05	36.7	39.8	0.003	30	0.04	0.8	105	124	18	3	2	2	1.5	3.0	19	0.01
KL40-05	39.8	42.1	0.0036	36	0.06	5	250	790	19	17	134	9	2.6	56.0	17	0.01
KL40-05	42.1	45	0.0028	28	0.01	0.8	299	540	12	6	4	3	1.8	5.5	28	0.01
KL40-05	45	49.3	0.0043	43	0.01	0.7	174	167	14	6	1	2	2	3.0	21	0.01
KL40-05	49.3	51.9	0.0034	34	0.02	2.9	520	1860	19	3	1	1	22	8.3	18	0.01
KL40-05	51.9	55.4	0.0029	29	0.22	4.8	1520	2200	62	4	2	3	15.4	16.0	31	0.45
KL40-05	55.4	59.6	0.0047	47	0.15	6.4	1440	1390	23	4	12	1	5.8	17.4	27	0.1
KL40-05	59.6	61.7	0.0054	54	0.07	3.3	3950	2300	20	7	3	1	14.5	5.5	19	0.12
KL40-05	61.7	64.7	0.001	10	0.03	1.5	480	990	12	3	1	1	3.7	3.8	13	0.01
KL40-05	64.7	67.7	0.0007	7	0.03	2.2	790	2090	13	5	0.01	1	9.8	4.8	16	0.01
KL40-05	67.7	70.7	0.0004	4	0.05	1.2	302	520	8	4	0.01	1	2.9	2.0	12	0.01
KL40-05	70.7	73.7	0.0026	26	0.02	1	241	357	7	7	0.01	1	1.9	1.8	12	0.01
KL40-05	73.7	76.7	0.0035	35	0.01	1.6	940	1170	8	2	0.01	1	2.4	3.0	11	0.01
KL40-05	76.7	79.7	0.0011	11	0.01	1.3	240	890	8	1	0.01	1	2.9	3.0	10	0.01
KL40-05	79.7	81.7	0.0021	21	0.04	1.6	420	770	6	1	0.01	1	2.8	2.3	12	0.01
KL40-05	81.7	84.9	0.0008	8	0.06	1.7	430	830	7	1	0.01	1	2.2	1.5	13	0.01
KL40-05	84.9	88.1	0.008	80	0.07	7.6	4300	5500	14	1	0.01	1	13.8	8.0	11	0.01
KL40-05	88.1	90.9	0.0044	44	0.04	2.8	337	1350	12	6	0.01	1	14	5.8	14	0.01
KL40-05	90.9	94.2	0.0085	85	0.03	1.3	306	420	8	1	0.01	1	1.8	0.8	13	0.01
KL40-05	94.2	96.5	0.0024	24	0.02	1.6	430	820	7	1	0.01	1	2.1	2.5	11	0.01
KL40-05	96.5	99.1	0.0045	45	0.02	2.5	530	840	13	1	0.01	1	8.9	1.5	10	0.01
KL40-05	99.1	102.3	0.0005	5	0.01	0.8	281	302	9	1	0.01	1	1.3	1.8	13	0.01
KL40-05	102.3	105.9	0.0007	7	0.08	1.3	320	253	7	2	0.01	1	2.1	3.5	14	0.01
KL40-05	105.9	108.6	0.0006	6	0.04	1.3	381	346	9	3	0.01	1	1.4	1.3	13	0.01
KL40-05	108.6	110.9	0.0032	32	0.08	3.9	950	2350	16	6	0.01	1	7	15.0	16	0.01
KL40-05	110.9	114.9	0.0007	7	0.02	1	430	349	12	2	0.01	1	1.3	2.2	16	0.01
KL40-05	114.9	117.4	0.0017	17	0.01	1	328	229	8	4	0.01	1	0.6	1.3	12	0.01
KL40-05	117.4	121.2	0.0022	22	0.01	1.2	262	470	9	2	0.01	1	1.1	2.0	15	0.01
KL40-05	121.2	123.4	0.0034	34	0.04	5.2	2300	4700	22	4	0.01	1	12.1	5.5	16	0.01
KL40-05	123.4	127	0.0003	3	0.03	1	420	249	12	2	0.01	1	1.4	2.3	15	0.01
KL40-05	127	129.9	0.0038	38	0.02	0.8	560	361	13	6	1	1	1.3	2.5	22	0.01
KL40-05	129.9	133.6	0.0026	26	0.03	1.6	810	670	16	4	0.01	1	3.3	3.3	19	0.01
KL40-05	133.6	136.7	0.0008	8	0.01	0.6	410	490	7	3	0.01	1	1.2	1.0	18	0.01
KL40-05	136.7	139.7	0.0193	193	0.03	11.4	7000	5900	47	1	1	1	36	9.3	18	0.15
KL40-05	139.7	145.7	0.74	7400	0.62	2.1	1080	103	160	18	2	17	18	17.8	108	0.01
KL40-05	145.7	148.6	0.0013	13	0.01	1.5	830	610	9	2	0.01	1	1.6	1.3	15	0.01
KL40-05	148.6	151.7	0.0111	111	0.22	46	40000	35000	320	6	4	1	62	36.3	29	0.88
KL40-05	151.7	154.7	0.0014	14	0.02	1.2	630	358	5	6	0.01	1	1.3	1.0	12	0.01
KL40-05	154.7	157.7	0.0012	12	0.01	1.4	750	377	6	3	0.01	1	1.1	1.5	17	0.01
KL40-05	157.7	160.7	0.0082	82	0.01	1.8	660	253	4	2	0.01	1	0.9	1.0	17	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL40-05	160.7	163.7	0.0019		19	0.02	3.4	3800	1830	45	2	0.01	1	7.3	4.8	15	0.1
KL40-05	163.7	166	0.0013		13	0.01	1.4	620	650	13	3	0.01	1	1.7	1.1	14	0.01
KL40-05	166	169.7	0.0188		188	0.05	1.7	530	870	20	12	0.01	1	2.9	1.8	17	0.01
KL40-05	169.7	172.2	0.068		680	0.05	1.3	610	383	22	24	2	1	1.4	2.5	24	0.01
KL40-05	172.2	175.5	0.0029		29	0.04	0.8	402	232	16	5	0.01	1	1.3	2.3	24	0.01
KL40-05	175.5	178.7	0.0014		14	0.02	1.2	770	450	21	2	0.01	1	1.5	3.9	17	0.01
KL40-05	178.7	181	0.0004		4	0.01	1.1	213	153	10	1	0.01	1	0.5	1.4	15	0.01
KL40-05	181	184	0.0005		5	0.01	0.5	294	279	9	2	0.01	1	1	2.8	20	0.01
KL40-05	184	186.6	0.0056		56	0.01	1.3	670	700	20	1	0.01	1	2.8	3.0	19	0.01
KL40-05	186.6	189.2	0.001		10	0.02	1	460	810	14	1	0.01	1	1.6	3.3	19	0.01
KL40-05	189.2	191.7	0.0017		17	0.02	1.8	910	1190	17	5	0.01	1	2.4	2.5	16	0.01
KL40-05	191.7	193.7	0.0082		82	0.02	1.4	1240	1330	7	5	0.01	1	2.9	3.0	18	0.01
KL40-05	193.7	196.1	0.003		30	0.02	0.6	386	420	17	3	0.01	1	2.1	1.4	17	0.01
KL40-05	196.1	199.7	0.0046		46	0.01	1.2	1140	650	5	3	0.01	1	1.4	1.8	14	0.01
KL40-05	199.7	202.2	0.0074		74	0.01	1.3	830	770	6	1	0.01	1	1.7	2.0	12	0.01
KL40-05	202.2	205.3	0.0029		29	0.01	0.8	630	620	4	3	0.01	2	1.3	4.3	16	0.01
KL40-05	205.3	208.4	0.0012		12	0.01	0.9	520	610	5	2	0.01	1	1.3	2.5	14	0.01
KL40-05	208.4	211.5	0.0025		25	0.02	2.7	1320	1690	14	1	0.01	1	5	4.8	15	0.01
KL40-05	211.5	214.6	0.0022		22	0.03	1.4	770	780	9	3	0.01	1	2.1	3.3	19	0.01
KL40-05	214.6	217.7	0.001		10	0.01	0.8	391	470	17	1	0.01	1	1.7	2.3	16	0.01
KL40-05	217.7	220.1	0.0011		11	0.01	0.6	353	306	9	3	0.01	2	0.9	1.5	17	0.01
KL40-05	220.1	223.7	0.0008		8	0.01	1.2	366	372	13	2	0.01	1	1.2	1.7	20	0.01
KL40-05	223.7	226.7	0.0341		341	0.02	87	40800	65100	64	2	5	1	100	14.5	18	0.15
KL40-05	226.7	229.7	0.0012		12	0.01	1.2	590	510	8	4	0.01	1	1.2	2.3	23	0.01
KL40-05	229.7	232.7	0.0013		13	0.01	1.4	700	680	17	4	0.01	1	1.8	4.3	20	0.01
KL40-05	232.7	234.8	0.0012		12	0.03	2.3	1190	1430	18	6	0.01	1	3	5.3	17	0.01
KL40-05	234.8	237.9	0.0037		37	0.03	4.7	3600	3300	27	3	0.01	2	6.2	13.5	14	0.01
KL40-05	237.9	240.4	0.0032		32	0.01	2.4	1360	1340	14	20	0.01	1	2.8	2.3	18	0.01
KL40-05	240.4	243.9	0.0012		12	0.01	1.8	830	1090	11	4	0.01	1	2.7	1.8	14	0.01
KL40-05	243.9	247.6	0.0031		31	0.01	7.9	4300	6200	28	3	0.01	1	9	5.3	13	0.01
KL40-05	247.6	250.7	0.0028		28	0.03	4	2400	2200	20	4	0.01	1	4.2	8.0	19	0.01
KL40-05	250.7	254.5	0.0013		13	0.01	4.3	1370	4100	13	3	0.01	1	5.3	4.2	21	0.01
KL40-05	254.5	258.8	0.0096		96	0.15	21.7	24700	15100	110	7	1	1	33	39.8	24	0.37
KL40-05	258.8	262.7	0.0016		16	0.01	0.1	480	253	5	4	0.01	1	1.5	0.8	13	0.01
KL40-05	262.7	265.7	0.0061		61	0.03	9.6	11200	8600	59	4	1	1	11.6	10.5	12	0.16
KL40-05	265.7	268.3	0.0068		68	0.07	7.3	5300	3020	68	7	0.01	1	9.9	9.5	15	0.1
KL40-05	268.3	270.5	0.0023		23	0.04	6.1	6900	3500	91	6	0.01	1	10.9	5.0	13	0.12
KL40-05	270.5	273.9	0.0121		121	0.07	10.1	10800	6600	160	8	0.01	1	19	10.8	16	0.13
KL40-05	273.9	277	0.0021		21	0.01	2.2	1630	1640	9	3	0.01	1	3.7	1.8	17	0.01
KL40-05	277	279.9	0.0023		23	0.01	6.2	6600	5600	12	7	0.01	1	6.1	10.3	12	0.01
KL40-05	279.9	282.7	0.0017		17	0.01	1.2	1680	830	11	10	0.01	1	1.7	3.1	12	0.01
KL40-05	282.7	284.8	0.0038		38	0.01	2.7	3500	3600	9	8	1	1	4.8	6.8	13	0.01
KL40-05	284.8	288.2	0.0028		28	0.01	1	1100	1060	12	23	0.01	1	2	5.5	10	0.01
KL40-05	288.2	291.4	0.0034		34	0.01	1.2	1420	560	7	6	2	2	1.6	3.8	15	0.01
KL40-05	291.4	294.6	0.0035		35	0.01	3.8	8900	4400	13	20	2	1	4.2	6.5	10	0.01
KL40-05	294.6	296.6	0.003		30	0.01	2	1520	1600	10	13	3	1	2.3	6.0	10	0.01
KL40-05	296.6	299.3	0.0068		68	0.01	7.8	3850	9900	12	24	5	1	10.1	22.5	9	0.01
KL40-05	299.3	302.2	0.0044		44	0.04	4	2340	1970	16	44	8	3	3.6	7.8	8	0.01
KL40-05	302.2	305	0.0086		86	0.01	3.9	3050	3340	16	59	3	2	6.5	10.9	18	0.01
KL40-05	305	307.5	0.0059		59	0.01	2.1	1160	1370	8	52	4	1	2.9	8.5	16	0.01
KL40-05	307.5	310.3	0.0037		37	0.01	1.7	460	470	7	43	5	2	1.5	8.0	15	0.01
KL40-05	310.3	313.5	0.0085		85	0.01	1	470	409	14	26	3	1	3.9	3.5	16	0.01
KL40-05	313.5	316.3	0.0345		345	0.04	11.3	1670	1020	98	206	55	1	18.7	17.5	20	0.01
KL40-05	316.3	318.3	0.012		120	0.01	2.2	310	201	27	64	14	1	4.7	7.3	14	0.01
KL40-05	318.3	321.5	0.279		2790	0.26	18.7	2830	1660	890	108	130	2	210	75.0	65	0.1
KL40-05	321.5	324.7	0.055		550	0.03	1.4	368	167	27	138	9	3	4.6	8.5	18	0.01
KL40-05	324.7	328.1	0.045		450	0.03	1	337	140	120	124	7	1	5.1	5.8	21	0.01
KL40-05	328.1	330.5	0.0408		408	0.01	1.7	1540	510	100	60	14	1	13	7.3	17	0.01
KL40-05	330.5	332.7	0.0163		163	0.01	0.8	480	282	25	192	9	1	5.7	4.3	18	0.01
KL40-05	332.7	335.5	0.0092		92	0.01	0.6	540	165	14	186	7	2	2	3.5	24	0.01
KL40-05	335.5	337.7	0.0074		74	0.01	1.1	550	154	18	133	15	2	5.2	5.0	20	0.01
KL40-05	337.7	340.7	0.0173		173	0.14	2.5	310	112	36	73	6	1	3.4	6.5	17	0.01
KL40-05	340.7	343.7	0.071		710	0.01	3.5	1950	298	35	45	18	1	2	7.3	26	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL40-06	197.2	199.4														
KL40-06	199.4	200.9														
KL40-06	200.9	203.9	0.73	7300	0.8	10.6	17600	3600	1070	36	4	32	116	11.5	15	0.36
KL40-06	203.9	206.9	0.112	1120	0.34	2.2	24300	580	160	47	6	73	18.3	9.5	22	0.25
KL40-06	206.9	209.9	0.131	1310	0.22	3.4	4850	1000	180	59	14	7	16	5.5	16	0.14
KL40-06	209.9	212.4	0.42	4200	0.21	4.2	7400	760	500	57	16	8	38	3.5	18	0.15
KL40-06	212.4	215.2	0.092	920	0.09	2	4310	690	110	33	9	1	8.5	3.7	12	0.12
KL40-06	215.2	217.7	0.0211	211	0.07	0.6	2000	237	29	115	3	1	1.4	2.0	14	0.01
KL40-06	217.7	220.5	0.114	1140	0.1	1.1	2900	165	50	33	5	3	2.3	4.5	14	0.01
KL40-06	220.5	221.7	0.71	7100	0.91	5.5	9100	154	63	209	6	21	9	26.8	30	0.01
KL40-06	221.7	224.6	1.19	11900	0.93	5.8	6100	335	250	91	2	69	10.3	16.0	24	0.1
KL40-06	224.6	227.7	0.46	4600	0.33	1.7	590	83	25	1040	2	12	2.1	5.5	46	0.01
KL40-06	227.7	230.2	1.03	10300	0.45	3.4	620	249	110	1220	1	15	2.9	6.5	20	0.01
KL40-06	230.2	233.3	3	30000	2.2	7.3	9400	256	230	317	1	72	11	15.0	84	0.12
KL40-06	233.3	234.7	3.29	32900	2.24	9.3	4200	430	260	262	1	55	13.4	19.0	49	0.01
KL40-06	234.7	236.7	2.02	20200	1.92	5.6	1350	51	59	750	1	35	11.1	16.0	49	0.01
KL40-06	236.7	239.7	2.43	24300	1.57	4.2	348	32	64	870	8	25	4.3	21.5	96	0.01
KL40-06	239.7	242.7	1.04	10400	1.87	3.1	252	22	36	80	4	36	4	15.0	34	0.01
KL40-06	242.7	245.9	1.45	14500	1.37	4.6	1680	315	21	108	2	27	7.1	8.5	34	0.01
KL40-06	245.9	248.9	1.46	14600	1.39	3.4	365	35	58	28	3	42	8.6	15.0	33	0.01
KL40-06	248.9	251.2	0.82	8200	0.84	2.3	710	32	62	21	2	54	5.9	11.8	31	0.01
KL40-06	251.2	254.4	0.935	9350	1.13	1.8	220	33	30	22	1	20	4.3	12.0	32	0.01
KL40-06	254.4	257.5	1.9	19000	1.03	3.8	2800	77	48	202	2	22	10.3	14.5	48	0.01
KL40-06	257.5	260	3.65	36500	1.01	5.6	275	123	160	2180	2	24	10.4	11.0	52	0.01
KL40-06	260	262.2	2.56	25600	1.59	3.6	190	61	190	1270	1	19	11.5	13.0	36	0.01
KL40-06	262.2	263.9	3.02	30200	1.12	3.5	240	50	35	216	1	28	4.6	16.0	31	0.01
KL40-06	263.9	266.9	0.8	8000	0.26	1.5	900	212	43	171	0.01	17	5.8	5.8	26	0.01
KL40-06	266.9	269.9	0.73	7300	0.17	1.3	196	32	24	802	0.01	14	2.3	4.9	23	0.01
KL40-06	269.9	272.9	1.35	13500	0.37	3.5	13200	1240	40	194	1	41	20	19.0	49	0.01
KL40-06	272.9	275.9	0.81	8100	0.31	1.2	9400	32	18	86	1	49	1.5	7.5	58	0.01
KL40-06	275.9	278.9	0.19	1900	0.09	0.6	156	24	16	172	1	17	1.3	3.0	32	0.01
KL40-06	278.9	281.4	0.52	5200	0.08	1	231	31	33	210	1	13	14.2	5.0	65	0.01
KL40-06	281.4	284.5	0.86	8600	0.28	1.2	9900	16	6	59	0.01	70	0.9	11.0	43	0.01
KL40-06	284.5	285.8	0.53	5300	0.5	1.3	10200	22	11	3	1	68	1.4	11.5	41	0.01
KL40-06	285.8	287.8	0.59	5900	0.35	1.1	700	33	6	49	2	45	1.3	4.3	30	0.01
KL40-06	287.8	290.8	0.28	2800	0.21	0.8	265	27	28	391	0.01	24	2.5	3.0	40	0.01
KL40-06	290.8	293.8	0.27	2700	0.1	0.8	132	43	27	294	0.01	16	1.7	3.3	21	0.01
KL40-06	293.8	296.6	0.42	4200	0.05	0.7	149	392	12	153	0.01	14	0.6	4.5	17	0.01
KL40-06	296.6	299.7	0.149	1490	0.03	0.7	223	113	10	137	0.01	8	1.2	2.5	25	0.01
KL40-06	299.7	302.7	0.37	3700	0.08	4.3	1640	940	31	309	0.01	11	4.7	4.3	29	0.01
KL40-06	302.7	305.7	0.49	4900	0.1	3.2	3840	3100	49	228	1	14	5.8	9.0	78	0.01
KL40-06	305.7	308.7	0.42	4200	0.08	3.2	3050	2600	59	101	5	8	3.7	11.0	26	0.01
KL40-06	308.7	311.3	0.975	9750	0.21	25.4	13600	12600	370	185	36	10	13.3	61.0	27	0.2
KL40-06	311.3	314.4	0.51	5100	0.14	7.6	3930	4000	50	158	6	8	3.4	15.0	24	0.01
KL40-06	314.4	317.5	0.35	3500	0.15	3.9	3250	2100	250	244	2	10	17.7	13.4	87	0.17
KL40-06	317.5	320.7	0.46	4600	0.21	1.1	237	89	34	241	1	19	1.3	4.3	30	0.01
KL40-06	320.7	323.7	0.354	3540	0.46	1.9	162	80	32	294	6	12	3.3	3.0	41	0.01
KL40-06	323.7	326.3	0.048	480	0.04	0.1	335	245	37	145	0.01	11	3.5	1.8	26	0.01
KL40-06	326.3	329.3	0.47	4700	0.13	5	1220	1700	350	1770	20	10	34	28.4	33	0.16
KL40-06	329.3	330.9	0.284	2840	0.17	2.6	690	580	140	3010	3	7	12	9.3	71	0.1
KL40-06	330.9	332.7	0.185	1850	0.08	2.3	500	317	28	1230	5	7	2	7.0	24	0.01
KL40-06	332.7	335.5	0.161	1610	0.11	2	540	336	20	1550	1	4	1.6	5.1	26	0.01
KL40-06	335.5	338.7	0.288	2880	0.08	1.5	138	129	18	2020	3	8	1.6	5.5	30	0.01
KL40-06	338.7	341.7	0.54	5400	0.37	1.2	194	69	18	12	0.01	14	0.8	5.3	28	0.01
KL40-06	341.7	344.7	0.27	2700	0.19	0.7	245	101	12	16	0.01	17	0.4	2.8	42	0.01
KL40-06	344.7	347.8	0.348	3480	0.21	1.1	356	239	12	164	0.01	17	0.3	3.0	28	0.01
KL40-06	347.8	350.9	0.38	3800	0.2	1.3	213	124	33	14	3	19	2.4	4.8	50	0.01
KL40-06	350.9	353.1	1.71	17100	0.58	2.5	1410	500	47	11	2	44	2.8	11.5	103	0.01
KL40-06	353.1	356.2	0.5	5000	0.4	1.4	4740	316	330	12	13	34	9	5.8	85	0.01
KL40-06	356.2	359.3	0.51	5100	0.57	3.5	590	900	380	14	10	31	6.5	8.0	47	0.01
KL40-06	359.3	362.4	1.76	17600	0.34	12.1	3900	5700	1050	475	27	27	6.9	15.0	97	0.01
KL40-06	362.4	365.5	0.75	7500	0.35	7.4	2200	3000	530	138	16	16	9.8	25.5	90	0.01
KL40-06	365.5	368.6	1.41	14100	0.63	2.8	2100	200	3300	271	0.01	51	14.1	8.0	65	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL40-06	368.6	371.7	1.52	15200	1.17	10.1	2200	3400	2150	46	1	36	21	15.5	67	0.01
KL40-06	371.7	374.7	1.21	12100	0.8	9.5	14200	6300	2200	10	0.01	21	17.2	15.0	42	0.01
KL40-06	374.7	377.7	0.38	3800	0.36	7.8	17800	7100	1060	4	0.01	18	8.4	16.5	28	0.01
KL40-06	377.7	379.5	0.17	1700	0.25	8.3	11600	8000	410	7	2	7	7.1	35.0	30	0.01
KL40-06	379.5	382.6	0.275	2750	0.52	63	16000	64800	700	6	2	12	35	62.0	24	0.88
KL40-06	382.6	385.2	0.5	5000	0.21	2.7	940	430	100	318	7	26	6.8	3.3	20	0.01
KL40-06	385.2	387.2	3.6	36000	0.81	4.5	950	130	16	12	2	73	5.3	3.0	18	0.01
KL40-06	387.2	388.9	2.46	24600	0.98	3	450	89	55	3	1	32	5.5	6.0	29	0.01
KL40-06	388.9	391.9	2.41	24100	0.99	6.3	1960	440	70	46	3	31	5.5	18.0	38	0.01
KL40-06	391.9	395.1	1.46	14600	1.22	9.6	5400	325	38	43	46	57	5.6	38.0	70	0.01
KL40-06	395.1	397.6	2.26	22600	1.44	14.3	2000	357	370	4	11	24	7	48.0	88	0.01
KL40-06	397.6	401.5	1.5	15000	1.01	12.1	2300	870	350	2	10	37	4.1	19.0	64	0.01
KL40-06	401.5	402.9	1.34	13400	0.62	7.6	2500	139	55	3	5	53	2.6	22.5	64	0.01
KL40-06	402.9	404.7	3.28	32800	0.86	13.1	990	450	61	10	1	68	6.5	19.0	68	0.01
KL40-06	404.7	407.7	3.67	36700	0.69	50	34400	27000	49	18	3	32	10.8	46.3	69	0.01
KL40-06	407.7	409.2	2.89	28900	0.61	72	50300	34800	85	409	7	15	11	80.0	95	0.01
KL40-06	409.2	410.7	0.37	3700	0.21	4.2	326	259	61	401	7	6	3.3	21.0	87	0.01
KL40-06	410.7	412.5	0.52	5200	0.07	5.4	2340	900	100	70	4	7	38	11.5	51	0.01
KL40-06	412.5	413.7	0.59	5900	0.1	7.2	310	352	35	162	32	4	3.5	32.2	62	0.01
KL40-06	413.7	416.7	0.46	4600	0.09	3.6	153	147	46	76	27	5	1.6	12.3	37	0.01
KL40-06	416.7	419.7	0.46	4600	0.08	2.3	83	84	70	77	5	4	2.1	12.0	23	0.01
KL40-06	419.7	422.7	0.37	3700	0.09	2.5	127	142	30	68	6	3	1.6	12.0	37	0.01
KL40-06	422.7	425.7	0.51	5100	0.2	2.1	367	263	40	116	6	6	1.9	16.4	48	0.01
KL40-06	425.7	428.7	0.473	4730	0.16	2.1	109	112	48	76	12	8	3.3	42.5	117	0.01
KL40-06	428.7	431.7	1.08	10800	0.24	3.2	260	184	24	80	5	5	2.4	24.5	67	0.01
KL40-06	431.7	434.7	0.79	7900	0.25	1.7	162	125	27	36	4	8	0.8	9.5	70	0.01
KL40-06	434.7	437.7	0.62	6200	0.27	1.4	103	84	80	96	4	8	2.8	32.0	54	0.01
KL40-06	437.7	440.7	0.306	3060	0.29	1.1	78	43	43	24	5	7	3.5	40.0	48	0.01
KL40-06	440.7	450.7	0.22	2200	0.09	3.6	3040	1700	230	67	1	9	20.3	9.8	30	0.01
KL40-06	450.7	452.7	0.214	2140	0.18	1.2	216	80	16	121	1	14	0.3	5.8	65	0.01
KL40-06	452.7	455	0.224	2240	0.15	1.1	55	25	3	43	0.01	5	0.2	3.8	65	0.01
KL40-06	455	457.5	0.354	3540	0.11	1	80	36	4	85	0.01	4	0.9	6.5	56	0.01
KL40-06	457.5	460.2	0.258	2580	0.18	0.9	112	74	3	22	1	4	1.1	5.5	57	0.01
KL40-06	460.2	461.7	1.43	14300	1.41	39.4	800	590	590	13	51	12	137	7.5	46	0.3
KL40-06	461.7	464.7	0.38	3800	0.35	1.7	244	97	22	10	2	7	0.5	7.8	58	0.01
KL40-06	464.7	467.7	0.382	3820	0.27	1.2	68	19	2	56	0.01	12	0.3	7.8	72	0.01
KL40-06	467.7	470.7	0.224	2240	0.16	1	61	31	10	15	1	8	3.4	5.3	63	0.01
KL40-06	470.7	473.7	0.324	3240	0.15	0.9	87	48	7	59	1	7	0.6	5.8	68	0.01
KL40-06	473.7	476.7	0.77	7700	0.26	2.2	400	388	81	59	2	7	0.8	9.7	84	0.01
KL40-06	476.7	479.7	0.376	3760	0.19	0.8	128	89	2	60	0.01	7	0.2	4.7	71	0.01
KL40-06	479.7	482.7	0.428	4280	0.27	0.9	96	48	24	13	0.01	9	0.7	8.8	54	0.01
KL40-06	482.7	485.7	0.43	4300	0.17	0.6	73	29	5	28	0.01	7	0.01	8.5	53	0.01
KL40-06	485.7	488.7	0.41	4100	0.18	1.7	190	50	3	60	3	6	0.01	6.8	34	0.01
KL40-06	488.7	491.7	0.8	8000	0.31	1.4	158	42	3	72	1	10	0.3	14.0	64	0.01
KL40-06	491.7	494.7	1.56	15600	0.32	2	142	53	11	174	0.01	9	0.2	3.0	83	0.01
KL40-06	494.7	497.7	0.47	4700	0.03	0.7	62	63	43	57	0.01	4	3.3	2.3	177	0.01
KL40-06	497.7	499.5	0.347	3470	0.13	3.2	101	115	37	111	4	13	6.8	20.0	91	0.01
KL40-06	499.5	501.6	0.67	6700	0.17	4.8	307	175	130	372	5	13	11.9	21.5	121	0.13
KL40-06	501.6	503.7	0.44	4400	0.12	5.1	76	114	6	65	2	6	0.8	4.8	55	0.01
KL40-06	503.7	506.7	0.61	6100	0.33	1.2	42	40	2	47	0.01	5	0.01	1.0	56	0.01
KL40-06	506.7	508.5	1	10000	0.66	1.1	62	19	1	59	0.01	9	0.01	2.0	35	0.01
KL40-06	508.5	510.2	0.6	6000	0.36	0.8	42	16	0.01	63	0.01	7	0.01	3.0	38	0.01
KL40-06	510.2	512.7	0.238	2380	0.01	0.6	47	25	2	32	0.01	4	0.01	1.6	123	0.01
KL40-06	512.7	515.1	0.351	3510	0.03	0.9	75	41	6	40	0.01	5	0.3	1.3	128	0.1
KL40-06	515.1	517.2	0.68	6800	0.51	1.1	60	38	8	72	0.01	8	0.01	1.8	71	0.01
KL40-06	517.2	519.4	0.39	3900	0.37	1.1	59	93	3	43	0.01	8	0.01	2.0	49	0.01
KL40-06	519.4	521.6	0.368	3680	0.16	1	54	43	1	121	0.01	5	0.01	2.3	88	0.01
KL40-06	521.6	524.6	0.384	3840	0.16	1.1	430	145	24	78	0.01	6	2	2.8	58	0.19
KL40-06	524.6	527.6	0.34	3400	0.04	1.1	58	37	5	189	1	5	0.2	5.5	60	0.01
KL40-06	527.6	530.6	0.26	2600	0.1	1.1	123	76	4	96	0.01	5	0.2	4.7	61	0.01
KL40-06	530.6	533.6	0.342	3420	0.06	1.6	124	57	3	102	0.01	6	0.01	2.5	80	0.01
KL40-06	533.6	536.6	0.33	3300	0.09	1.4	78	45	2	178	1	5	0.01	3.3	57	0.01
KL40-06	536.6	539.6	0.46	4600	0.12	2	89	47	2	80	2	6	0.01	2.8	73	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL40-06	539.6	542.6	0.64	6400	0.37	9.2	374	404	12	173	12	5	2	5.8	69	0.16
KL40-06	542.6	545.6	0.34	3400	0.04	1.1	97	73	1	99	0.01	10	0.01	2.3	65	0.01
KL40-06	545.6	548.6	0.26	2600	0.04	1.2	59	74	5	44	0.01	5	0.7	2.5	56	0.01
KL40-06	548.6	551.6	0.28	2800	0.1	1.5	45	21	12	127	0.01	4	1.2	5.3	81	0.01
KL40-06	551.6	554.6	0.346	3460	0.31	2.3	46	34	4	138	2	4	0.5	3.3	106	0.01
KL40-06	554.6	557.6	0.46	4600	0.27	3	378	158	8	61	7	3	0.7	2.3	69	0.01
KL40-06	557.6	560.6	0.55	5500	0.32	2.5	84	131	44	122	4	5	15.1	1.5	76	0.01
KL40-06	560.6	563.6	2.23	22300	1.48	16	690	2900	2880	66	9	14	362	0.0	187	0.46
KL40-06	563.6	566.6	1	10000	1.43	11.8	64	78	1340	117	8	16	188	36.3	115	0.25
KL40-06	566.6	569.6	0.433	4330	0.13	1.8	28	37	190	46	2	7	11.7	5.0	192	0.01
KL40-06	569.6	572.6	0.21	2100	0.14	2	46	54	66	47	3	7	6.4	8.3	121	0.11
KL40-06	572.6	575.6	0.356	3560	0.17	5.4	42	40	11	113	7	5	1.2	7.5	154	0.01
KL40-06	575.6	577.6	0.26	2600	0.05	1.7	62	25	4	28	1	3	0.6	2.8	161	0.01
KL40-06	577.6	579.8	0.276	2760	0.05	1.7	27	15	5	258	2	8	0.8	7.6	52	0.01
KL40-06	579.8	581.6	0.214	2140	0.05	1.1	38	32	4	94	2	5	1	3.0	78	0.01
KL40-06	581.6	584.6	0.244	2440	0.03	0.7	67	42	7	46	0.01	4	1.7	2.8	73	0.01
KL40-06	584.6	587.6	0.21	2100	0.04	0.6	86	52	4	98	0.01	4	0.8	3.8	82	0.01
KL40-06	587.6	590.6	0.22	2200	0.05	0.6	96	48	3	81	0.01	5	0.4	2.3	97	0.01
KL40-06	590.6	593.6	0.374	3740	0.08	1.3	123	183	5	117	0.01	4	0.6	3.3	76	0.01
KL40-06	593.6	596.6	0.33	3300	0.18	2.1	31	21	10	46	4	2	0.9	1.3	158	0.01
KL40-06	596.6	599.6	0.43	4300	0.19	2.6	14	14	5	82	3	3	0.7	1.0	171	0.01
KL40-06	599.6	602.6	0.3	3000	0.04	1.8	29	15	9	99	2	2	3	1.5	141	0.01
KL40-06	602.6	605.6	0.262	2620	0.09	1.8	88	43	12	59	2	3	1	4.9	148	0.01
KL40-06	605.6	608.6	0.206	2060	0.02	1.2	56	19	17	138	1	2	1.6	2.5	167	0.01
KL40-06	608.6	611.6	0.21	2100	0.11	2.1	78	64	8	89	4	2	1.1	3.5	186	0.01
KL40-06	611.6	614.6	0.26	2600	0.07	1.6	18	19	6	29	2	2	2	2.5	128	0.01
KL40-06	614.6	617.6	0.26	2600	0.06	1.6	54	25	9	87	1	3	4.4	3.2	175	0.01
KL40-06	617.6	619.4	0.32	3200	0.14	2.5	34	23	50	77	1	3	28	4.0	146	0.01
KL40-06	619.4	622.5	0.284	2840	0.1	1.3	15	17	14	126	1	2	6.3	2.8	178	0.01
KL40-06	622.5	623.6	0.36	3600	0.11	2.6	46	34	34	119	3	2	10.4	2.3	149	0.01
KL40-06	623.6	626.6	0.32	3200	0.14	1.7	43	24	100	59	3	2	16.3	3.2	155	0.01
KL40-06	626.6	629.6	0.364	3640	0.11	1.4	32	19	33	24	0.01	3	6.2	3.5	158	0.15
KL40-06	629.6	632.6	0.343	3430	0.07	0.8	118	132	28	41	0.01	4	1.6	2.0	143	0.01
KL40-06	632.6	635.6	0.23	2300	0.12	1	23	26	11	138	1	2	1.5	2.5	121	0.01
KL40-06	635.6	638.6	1.03	10300	1.2	8.7	650	135	1600	53	7	5	215	6.5	100	0.7
KL40-06	638.6	641.6	0.308	3080	0.19	2.1	357	103	33	69	4	6	6.5	4.3	85	0.01
KL40-06	641.6	644.6	0.28	2800	0.16	2.2	114	43	640	98	5	5	45	5.8	103	0.01
KL40-06	644.6	647.6	1.37	13700	0.49	3.5	60	61	1440	59	4	4	168	2.0	117	0.2
KL40-06	647.6	649.8	0.98	9800	0.47	3.5	21	34	660	760	4	5	70	2.0	141	0.13
KL40-06	649.8	652.9	0.28	2800	0.13	1.7	132	75	95	299	2	2	18	2.8	104	0.01
KL40-06	652.9	654	0.6	6000	1.12	9.3	204	172	1840	3820	9	7	257	8.8	130	0.3
KL40-06	654	656.6	2.01	20100	2.08	12.5	50	168	6000	970	3	6	880	8.0	124	0.59
KL40-06	656.6	658.5	0.92	9200	0.8	4.3	104	119	2230	130	2	2	255	2.3	139	0.21
KL40-06	658.5	661.6	0.57	5700	0.29	2.4	54	69	260	65	3	2	16	2.0	125	0.22
KL40-06	661.6	664.7	0.34	3400	0.14	1.5	78	50	140	67	2	4	14	2.8	136	0.01
KL40-06	664.7	667.8	0.65	6500	0.18	1.8	69	39	3	68	1	4	0.01	3.3	123	0.01
KL40-06	667.8	670.8	0.294	2940	0.05	1.2	88	53	19	53	1	3	3.6	3.0	109	0.01
KL40-06	670.8	673.9	0.32	3200	0.03	1.5	183	112	15	49	0.01	2	0.6	2.5	94	0.01
KL40-06	673.9	677	0.3	3000	0.04	0.8	48	30	12	82	1	6	0.5	10.4	73	0.01
KL40-06	677	678.5	0.38	3800	0.04	1.6	210	102	4	22	0.01	3	0.4	3.5	116	0.01
KL40-06	678.5	680.6	0.25	2500	0.03	1.3	252	112	6	37	0.01	2	0.5	2.8	129	0.12
KL40-06	680.6	683.6	0.24	2400	0.02	1.1	93	61	12	279	0.01	2	0.6	2.5	126	0.01
KL40-06	683.6	686.6	0.21	2100	0.02	1.2	131	65	3	107	1	3	0.3	2.0	104	0.01
KL40-06	686.6	689.6	0.21	2100	0.02	1.2	80	48	2	44	2	2	0.5	2.3	115	0.01
KL40-06	689.6	692.6	0.146	1460	0.03	0.9	145	67	2	42	2	2	0.4	2.5	99	0.01
KL40-06	692.6	695.6	0.162	1620	0.03	0.1	178	103	3	43	1	5	0.6	8.5	124	0.01
KL40-06	695.6	698.6	0.282	2820	0.03	1.1	253	125	15	245	1	5	4.2	3.3	102	0.01
KL40-06	698.6	701.6	0.21	2100	0.01	1.5	131	104	6	123	1	3	2.8	2.5	101	0.01
KL40-06	701.6	704.6	0.137	1370	0.01	1	93	63	27	309	2	2	3.5	3.3	115	0.01
KL40-06	704.6	707.6	0.082	820	0.08	1.3	61	36	24	156	4	2	0.7	3.5	97	0.01
KL40-06	707.6	710.6	0.108	1080	0.01	1	45	25	16	119	2	3	0.8	1.8	104	0.01
KL40-06	710.6	712.2	0.22	2200	0.02	1.3	79	40	4	211	1	4	0.3	3.0	125	0.01
KL40-06	712.2	714.4	0.22	2200	0.05	1.2	143	93	3	112	1	4	0.5	1.5	91	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL40-06	714.4	716.6	0.185	1850	0.04	0.8	154	100	2	114	0.01	5	0.3	1.5	57	0.01
KL40-06	716.6	719.6	0.19	1900	0.03	1.3	137	86	1	227	1	4	0.7	3.3	44	0.01
KL40-06	719.6	722.6	0.145	1450	0.02	1.2	138	100	5	251	0.01	4	1.7	1.8	87	0.01
KL40-06	722.6	725.6	0.24	2400	0.04	2	325	198	11	76	2	3	7.1	4.6	95	0.01
KL40-06	725.6	728.6	0.21	2100	0.03	1.8	700	395	12	80	2	4	8.2	4.0	96	0.1
KL40-06	728.6	731.6	0.284	2840	0.03	1.7	206	153	13	51	0.01	4	15.7	3.2	114	0.01
KL40-06	731.6	734.6	0.187	1870	0.04	1.9	226	118	7	118	2	3	2.4	2.5	122	0.01
KL40-06	734.6	737.6	0.184	1840	0.03	1.8	89	59	13	65	2	4	2.4	2.8	137	0.01
KL40-06	737.6	740.6	0.22	2200	0.03	1.1	195	116	28	32	1	3	2.5	1.0	76	0.01
KL40-06	740.6	743.6	0.193	1930	0.03	0.9	133	67	10	73	1	5	0.3	1.3	62	0.01
KL40-06	743.6	746.6	0.96	9600	0.54	3.5	301	99	24	92	9	4	7.8	4.0	73	0.01
KL40-06	746.6	749.6	0.152	1520	0.03	0.7	128	81	5	34	0.01	5	0.4	2.0	58	0.01
KL40-06	749.6	752.6	0.184	1840	0.04	0.9	83	43	67	81	2	4	0.2	1.3	68	0.01
KL40-06	752.6	755.6	0.167	1670	0.03	0.9	124	57	8	146	1	5	0.01	1.3	70	0.01
KL40-06	755.6	758.6	0.124	1240	0.01	0.7	109	71	1	167	0.01	5	0.01	1.0	69	0.01
KL40-06	758.6	761.6	0.168	1680	0.04	0.8	103	52	1	58	3	6	0.01	1.0	43	0.01
KL40-06	761.6	763.8	0.123	1230	0.03	0.7	108	47	2	43	0.01	7	0.01	1.5	53	0.01
KL40-06	763.8	766	0.188	1880	0.06	0.6	51	21	1	25	1	7	0.01	2.0	33	0.01
KL40-06	766	767.6	0.212	2120	0.08	0.6	91	40	6	44	2	6	0.3	2.3	98	0.01
KL40-06	767.6	770.6	0.165	1650	0.03	0.7	40	16	3	520	1	3	0.4	3.3	134	0.01
KL40-06	770.6	773	0.364	3640	0.07	1.9	61	35	5	331	1	5	0.7	3.3	62	0.01
KL40-06	773	775.6	0.256	2560	0.04	0.8	62	29	1	44	1	5	0.01	2.0	61	0.01
KL40-06	775.6	778.5	0.39	3900	0.07	1.2	48	24	2	106	2	10	0.2	2.0	68	0.01
KL40-06	778.5	779.6	0.24	2400	0.06	0.8	44	13	2	47	1	5	0.01	2.1	110	0.01
KL40-06	779.6	782.6	0.29	2900	0.28	1.8	1540	620	220	620	4	8	45	6.5	128	0.1
KL40-06	782.6	785.6	0.27	2700	0.07	1.4	91	65	8	85	2	4	1.7	4.1	87	0.01
KL40-06	785.6	788.6	0.31	3100	0.07	1.1	87	44	3	50	1	7	0.6	1.8	158	0.01
KL40-06	788.6	791.6	0.23	2300	0.05	1.2	118	61	8	158	1	8	1.4	3.6	150	0.01
KL40-06	791.6	794.6	0.22	2200	0.05	1	101	44	7	142	2	4	1.1	3.0	100	0.01
KL40-06	794.6	797.6	0.183	1830	0.04	0.8	56	22	9	39	1	3	4.5	1.0	35	0.01
KL40-06	797.6	800.6	0.36	3600	0.13	1.5	201	74	37	11	2	5	16.8	1.8	31	0.01
KL40-06	800.6	803.6	0.24	2400	0.09	0.7	80	32	2	203	1	7	0.01	1.5	123	0.01
KL40-06	803.6	806.6	0.193	1930	0.04	0.7	34	17	21	16	1	7	1.8	2.5	118	0.01
KL40-06	806.6	808.6	0.133	1330	0.01	23.7	28	8	4	89	1	24	0.9	3.1	90	0.01
KL40-07	0	3	0.0275	275	0.04	1	250	99	13	1	1	1	1.5	1.2	21	0.01
KL40-07	3	5.7	0.0101	101	0.01	1.3	320	134	17	4	3	1	2.4	2.0	22	0.01
KL40-07	5.7	8.7	0.0055	55	0.02	0.7	302	146	11	1	1	1	2.3	0.0	26	0.01
KL40-07	8.7	11.2	0.0062	62	0.11	1.7	580	176	26	1	0.01	1	18	1.2	23	0.11
KL40-07	11.2	13.7	0.0039	39	0.01	1.1	404	320	19	4	1	1	3.5	1.2	20	0.01
KL40-07	13.7	14.7	0.0057	57	0.04	2	940	750	17	4	4	1	3.7	3.1	22	0.01
KL40-07	14.7	17.7	0.0077	77	0.01	1.5	470	340	22	6	4	1	2.2	3.2	28	0.01
KL40-07	17.7	20.7	0.0088	88	0.03	1.7	830	267	49	9	3	1	7.5	1.5	25	0.01
KL40-07	20.7	23.7	0.0234	234	0.02	1.1	156	127	60	38	16	1	2.2	1.0	42	0.01
KL40-07	23.7	26.7	0.0099	99	0.06	0.8	362	112	88	24	17	1	10.5	0.8	39	0.01
KL40-07	26.7	29.7	0.0213	213	0.02	1.7	430	234	60	24	46	1	15.5	2.3	36	0.01
KL40-07	29.7	32.7	0.0324	324	0.02	1.5	146	76	56	52	12	1	3.3	1.5	42	0.01
KL40-07	32.7	35.2	0.0197	197	0.04	0.9	331	75	38	14	10	1	3.3	0.8	31	0.01
KL40-07	35.2	38.2	0.0075	75	0.12	0.6	146	56	44	10	5	1	3.3	0.0	35	0.01
KL40-07	38.2	41.3	0.0188	188	0.05	0.8	345	68	36	13	7	1	2.9	1.2	33	0.01
KL40-07	41.3	44.4	0.0102	102	0.05	1.5	367	146	75	12	22	2	5.6	1.0	32	0.01
KL40-07	44.4	47.5	0.0052	52	0.01	1.3	420	1340	30	19	2	1	3.4	2.9	30	0.01
KL40-07	47.5	50.6	0.0094	94	0.05	1.6	364	140	55	14	24	1	5.3	1.2	32	0.01
KL40-07	50.6	53.7	0.0057	57	0.01	1	440	1370	32	20	3	1	3.6	2.0	30	0.01
KL40-07	53.7	56.7	0.014	140	0.1	0.9	1160	249	130	18	4	1	4.2	1.2	37	0.16
KL40-07	56.7	59.7	0.0133	133	0.11	1	1180	223	130	16	5	1	4.1	1.8	35	0.19
KL40-07	59.7	61.1	0.109	1090	0.07	21.9	6800	5800	140	9	86	5	9.8	11.7	35	0.16
KL40-07	61.1	63.4	0.111	1110	0.06	22.2	7200	5700	130	8	85	5	11.6	12.3	37	0.2
KL40-07	63.4	65.7	0.0255	255	0.12	1.8	610	305	100	10	20	11	4.4	7.5	19	0.11
KL40-07	65.7	68.7	0.0272	272	0.12	1.6	660	292	110	12	22	12	5.5	6.8	20	0.13
KL40-07	68.7	71.7	0.0202	202	0.13	1.4	1050	268	100	12	6	3	7.7	4.3	35	0.1
KL40-07	71.7	74.7	0.0198	198	0.13	1.7	1060	249	90	10	5	3	7.6	3.8	30	0.12
KL40-07	74.7	77.7	0.0101	101	0.07	2.5	670	560	120	22	12	1	30.5	6.3	37	0.01
KL40-07	77.7	80.7	0.0329	329	0.05	4.2	5980	2300	120	8	8	2	23.5	10.3	38	0.32

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL40-07	80.7	83.7	0.0323	323	0.05	4	6300	2370	130	7	10	2	24	10.8	41	0.27
KL40-07	83.7	86.7	0.0294	294	0.39	3	2210	670	150	54	40	4	54	12.8	90	0.33
KL40-07	86.7	89.7	0.0297	297	0.4	2.7	2240	680	160	56	44	4	56	12.7	91	0.33
KL40-07	89.7	91.2	0.0027	27	0.12	0.6	334	85	52	134	4	4	4.6	2.2	86	0.01
KL40-07	91.2	92.7	0.075	750	0.21	1	610	252	57	256	7	4	5.4	5.0	92	0.01
KL40-07	92.7	94.8	0.0045	45	0.13	0.7	1150	300	26	135	1	3	2.5	2.0	84	0.01
KL40-07	94.8	96.6	0.077	770	0.2	1.2	610	231	59	266	5	5	4.9	4.3	85	0.01
KL40-07	96.6	98.7	2.24	22400	1.76	13.3	2500	1140	1780	930	47	30	530	28.5	137	0.78
KL40-07	98.7	100.6	2.26	22600	1.72	13.9	2400	1070	1770	910	49	32	540	30.5	123	0.86
KL40-07	100.6	101.7	0.0349	349	0.27	4.6	2230	870	120	460	20	3	12.1	20.0	40	0.1
KL40-07	101.7	104.7	0.0165	165	0.2	1.5	1920	590	92	50	6	5	5.3	8.0	50	0.01
KL40-07	104.7	106.8	0.0162	162	0.24	2.2	2560	610	89	28	8	5	8.1	8.8	22	0.01
KL40-07	106.8	108.8	0.0061	61	0.16	0.1	690	106	87	127	0.01	1	6.2	3.8	21	0.01
KL40-07	108.8	110.3	0.332	3320	0.9	17.6	9300	1430	290	739	42	5	52	15.3	50	0.88
KL40-07	110.3	111.7	0.323	3230	0.93	17.4	9900	1410	310	730	44	5	52	14.6	45	0.96
KL40-07	111.7	113.7	0.148	1480	1.3	15.6	1490	540	460	837	40	2	40	11.5	152	1.03
KL40-07	113.7	116.7	0.148	1480	1.38	15.9	1490	510	450	856	33	2	36	9.8	162	0.98
KL40-07	116.7	119.7	0.055	550	1.65	23.9	12000	2600	400	1160	80	7	13.1	16.0	53	1.06
KL40-07	119.7	122.7	0.106	1060	1.49	8.3	14500	3000	590	1170	23	7	62	18.5	145	0.96
KL40-07	122.7	125.7	0.105	1050	1.48	8.2	14600	2900	610	1190	26	7	56	18.5	142	0.9
KL40-07	125.7	127.6	0.123	1230	0.43	4.6	23000	2800	360	213	25	9	26	24.7	70	0.9
KL40-07	127.6	130.8	0.121	1210	0.45	4.7	22900	2700	370	211	24	10	26	24.5	70	0.96
KL40-07	130.8	132.3	0.133	1330	0.61	5.4	39800	4000	400	386	39	16	19.5	27.5	61	1
KL40-07	132.3	134.4	0.0065	65	0.09	1	7000	640	23	33	5	1	2.3	5.2	30	0.14
KL40-07	134.4	135.6	0.0066	66	0.09	0.8	6900	610	23	33	4	1	2.1	5.8	29	0.15
KL40-07	135.6	137.7	0.0096	96	0.1	0.9	4280	384	35	29	3	1	2	4.0	33	0.18
KL40-07	137.7	140.7	0.0099	99	0.06	0.7	1320	156	25	43	1	1	2.4	2.0	29	0.01
KL40-07	140.7	143.7	0.0107	107	0.06	0.7	1340	148	25	45	1	1	2.3	2.3	30	0.01
KL40-07	143.7	146.4	0.0089	89	0.09	1.3	1980	540	35	32	4	1	1.4	5.0	28	0.11
KL40-07	146.4	149.7	0.0186	186	0.37	1.9	2680	580	190	76	4	2	3.9	6.0	92	0.37
KL40-07	149.7	152	0.171	1710	0.2	2.4	1800	197	460	57	1	3	4	6.0	37	0.01
KL40-07	152	153.7	0.169	1690	0.2	2.3	1780	196	450	55	1	3	4.2	5.8	34	0.1
KL40-07	153.7	155.7	0.128	1280	0.19	2.1	670	42	40	2450	22	1	2.6	7.5	35	0.01
KL40-07	155.7	157.7														
KL40-07	157.7	159.2	0.0072	72	0.1	0.5	510	75	33	2730	18	1	3.9	6.0	52	0.01
KL40-07	159.2	161.2	0.335	3350	1.23	8.8	39700	201	270	2150	142	27	6.5	47.3	78	0.3
KL40-07	161.2	162.8	0.0236	236	0.22	1.3	6500	91	57	51	26	3	17.4	9.0	16	0.28
KL40-07	162.8	164.7	0.0248	248	0.24	1.2	6500	96	57	48	23	3	17.6	9.5	15	0.21
KL40-07	164.7	167.1	0.0144	144	0.27	2.7	1700	283	63	142	20	1	1.9	6.0	19	0.2
KL40-07	167.1	169.3	0.0182	182	0.15	0.7	5310	104	62	31	7	1	1.2	5.8	14	0.18
KL40-07	169.3	172.1	0.0133	133	0.17	0.8	2780	91	51	25	12	1	0.7	4.0	14	0.39
KL40-07	172.1	174.5	0.0131	131	0.17	0.8	2610	96	53	21	14	1	0.9	4.0	15	0.35
KL40-07	174.5	177.3	0.116	1160	0.25	1.9	7200	310	370	54	16	1	5.3	9.8	16	0.37
KL40-07	177.3	180.5	0.118	1180	0.25	2	7100	311	410	58	18	2	5.2	9.3	17	0.33
KL40-07	180.5	183.7	0.0289	289	0.51	1	1600	178	110	83	20	2	2.7	5.0	22	0.1
KL40-07	183.7	186.5	0.086	860	0.51	1.3	2710	204	210	34	20	3	3.3	6.3	17	0.01
KL40-07	186.5	188.7	0.087	870	0.48	1.2	2790	210	210	36	22	3	2.7	6.5	16	0.1
KL40-07	188.7	189.8	0.155	1550	0.8	3	7200	540	410	29	26	8	13.5	7.0	18	0.11
KL40-07	189.8	191.6	0.162	1620	0.83	3	7000	590	420	27	22	8	13	5.8	19	0.1
KL40-07	191.6	194.7	0.3	3000	1.24	1.8	620	91	190	43	62	21	8.8	29.3	26	0.01
KL40-07	194.7	197.7	0.91	9100	2.12	5.3	184	48	47	42	40	45	5.9	37.0	31	0.01
KL40-07	197.7	200.7	0.76	7600	1.65	6.4	138	33	200	26	24	34	4.2	23.5	42	0.01
KL40-07	200.7	203.7	1.22	12200	2.42	6.8	124	26	48	112	3	29	8.3	13.5	34	0.01
KL40-07	203.7	206.7	1.39	13900	3.06	5.4	165	35	300	171	7	28	9.4	34.8	35	0.01
KL40-07	206.7	209.7	1.2	12000	1.77	4.9	142	27	49	187	4	31	6.1	22.5	30	0.01
KL40-07	209.7	212.7	1.15	11500	1.76	4.5	145	29	40	182	3	33	5.9	23.5	30	0.01
KL40-07	212.7	215.7	0.85	8500	1.92	3.1	267	84	230	52	0.01	36	7.1	16.3	39	0.01
KL40-07	215.7	218.7	1.08	10800	1.16	6.8	6100	750	740	132	20	41	8.6	18.9	84	0.82
KL40-07	218.7	221.7	1.02	10200	0.72	9.1	3000	1630	1850	1140	10	63	4.5	25.0	80	0.54
KL40-07	221.7	224.7	1	10000	0.7	8.9	3000	1600	1800	1080	11	61	4.2	25.0	78	0.56
KL40-07	224.7	227.7	0.51	5100	0.4	8.2	1320	420	600	620	7	28	4.5	7.0	68	0.1
KL40-07	227.7	230.7	1.25	12500	1.26	5	1010	407	410	999	5	47	5.6	13.5	40	0.01
KL40-07	230.7	232.9	1.24	12400	1.28	4.9	1000	380	430	990	7	49	5.1	12.5	39	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL40-07	232.9	235	1.9	19000	1.78	5.7	188	54	42	257	2	47	3.5	12.0	63	0.01
KL40-07	235	236.7	0.66	6600	0.58	2.1	290	55	58	120	1	20	2.9	6.5	19	0.01
KL40-07	236.7	239.7	0.64	6400	0.6	1.8	300	49	55	122	0.01	20	2.9	5.8	18	0.01
KL40-07	239.7	242.7	0.306	3060	0.35	1.2	81	37	14	120	1	13	1.2	5.5	17	0.01
KL40-07	242.7	245.7	0.56	5600	0.66	1.9	103	22	27	78	1	51	2.6	9.5	20	0.01
KL40-07	245.7	248.4	0.84	8400	1.03	2.8	138	31	300	71	0.01	35	4.2	7.3	48	0.01
KL40-07	248.4	251.7	0.75	7500	1	2.7	530	154	170	73	0.01	28	3.6	8.4	146	0.01
KL40-07	251.7	254.7	0.136	1360	0.03	0.1	104	51	6	37	0.01	14	1.2	2.1	34	0.01
KL40-07	254.7	257.7	0.99	9900	0.64	8	935	362	130	546	9	36	3.9	9.5	33	0.01
KL40-07	257.7	260.7	0.97	9700	0.66	8.2	1175	384	120	530	10	35	3.5	8.3	30	0.01
KL40-07	260.7	263.6	0.292	2920	0.15	5	660	338	51	660	1	13	3.4	3.8	21	0.01
KL40-07	263.6	266.6	0.298	2980	0.16	4.9	660	357	52	650	2	15	3.6	4.0	20	0.01
KL40-07	266.6	269.7	0.62	6200	0.56	5.8	344	128	130	560	12	41	2.4	7.8	40	0.01
KL40-07	269.7	272.7	0.75	7500	1.28	8.4	850	384	1050	126	44	29	1.7	8.5	82	0.01
KL40-07	272.7	275	1.4	14000	1.16	21.6	1780	620	4200	84	12	28	1.2	14.5	148	0.01
KL40-07	275	277	1.37	13700	0.86	12.7	1580	450	2500	128	6	19	1.3	19.0	76	0.01
KL40-07	277	278.7	2.26	22600	1.54	27.5	3480	720	4350	120	6	50	2.8	24.0	53	0.12
KL40-07	278.7	281.7	2.98	29800	1.58	12.4	1720	369	1390	1320	3	45	3.2	27.5	52	0.01
KL40-07	281.7	284.7	2.17	21700	1.2	15.4	1920	540	230	628	5	53	2	22.5	42	0.01
KL40-07	284.7	287.7	1.04	10400	1.38	21.2	1210	306	800	84	18	29	1.9	17.0	53	0.11
KL40-07	287.7	290.7	1.58	15800	1.34	14.3	8300	470	370	17	42	32	3.4	26.0	63	0.1
KL40-07	290.7	293.7	1.92	19200	1.88	16	1520	362	51	92	42	41	5.9	23.0	54	0.01
KL40-07	293.7	296.7	1.44	14400	2.59	6	670	136	34	8	10	72	3	9.8	35	0.01
KL40-07	296.7	299.7	2.47	24700	1.4	14.9	430	96	16	75	7	56	2.2	36.0	83	0.01
KL40-07	299.7	302.7	1.8	18000	1.24	7.3	106	43	10	16	12	21	2.2	20.0	83	0.01
KL40-07	302.7	305.7	1.63	16300	1.36	6.1	133	62	20	33	14	18	2.6	24.0	63	0.01
KL40-07	305.7	308.7	3.06	30600	2.3	12	101	60	18	86	8	37	1.7	24.0	71	0.75
KL40-07	308.7	311.7	2.91	29100	3.52	9.2	47	19	9	197	4	36	0.5	21.0	58	0.1
KL40-07	311.7	314.7	2.41	24100	1.8	7.2	408	40	26	148	4	36	0.8	31.5	86	0.17
KL40-07	314.7	317.7	2.36	23600	2.04	7.7	120	29	8	112	5	38	0.9	40.0	52	0.01
KL40-07	317.7	320.7	3.79	37900	3.12	9.1	171	48	14	95	2	48	1.1	57.5	83	1.32
KL40-07	320.7	323.7	2.98	29800	2.42	8.9	344	73	42	22	6	47	1.5	48.5	77	2.85
KL40-07	323.7	326.7	3.32	33200	2.16	10.8	256	50	43	23	3	45	2.2	32.5	133	1.44
KL40-07	326.7	329.7	1.91	19100	1.34	6.2	168	46	9	9	6	51	0.8	30.0	74	0.62
KL40-07	329.7	332.7	2.67	26700	1.68	7.9	60	24	4	43	3	52	0.3	25.0	72	0.01
KL40-07	332.7	335.7	1.51	15100	1.74	4.2	2820	870	330	60	4	37	0.6	25.7	197	0.13
KL40-07	335.7	338.7	2.14	21400	1.36	6.2	127	43	11	73	5	60	0.6	23.5	111	0.01
KL40-07	338.7	341.7	4.17	41700	2.62	8.3	242	28	6	193	2	56	0.9	30.0	83	0.01
KL40-07	341.7	344.7	4.51	45100	2.78	8.4	284	36	2	49	2	77	0.9	42.5	122	0.01
KL40-07	344.7	347.2	4.45	44500	2.3	8.2	192	31	0.01	87	1	73	0.4	47.5	84	0.01
KL40-07	347.2	350.3	3.73	37300	2.12	8.2	295	24	0.01	106	1	67	0.8	40.0	42	0.01
KL40-07	350.3	353.5	3.94	39400	1.92	9.6	358	76	20	47	4	50	2.2	35.0	41	0.01
KL40-07	353.5	356.6	5	50000	3.2	13.8	10000	740	62	199	6	64	3.3	45.0	62	0.01
KL40-07	356.6	359.7	4.25	42500	3.22	10.8	265	28	18	93	3	48	1.4	32.5	59	0.01
KL40-07	359.7	362.7	3.39	33900	2.82	11.9	580	50	15	95	5	52	1.5	27.0	131	0.01
KL40-07	362.7	365.7	5	50000	4.4	11.5	1070	58	8	14	1	64	1.6	32.5	77	0.01
KL40-07	365.7	368.7	5	50000	3.2	13.1	930	43	6	10	2	77	1.3	31.3	48	0.01
KL40-07	368.7	371.7	4.11	41100	2.52	11.3	440	30	9	50	2	54	1.1	25.0	65	0.01
KL40-07	371.7	374.7	3.63	36300	2.52	11.8	133	44	9	55	2	65	2.5	17.5	79	0.01
KL40-07	374.7	377.7	3.12	31200	2	8.6	99	34	10	38	3	54	2.7	25.0	65	0.01
KL40-07	377.7	380.7	2.24	22400	1.76	10.8	114	53	15	71	7	33	2.1	21.0	85	0.01
KL40-07	380.7	383.7	3.44	34400	2.24	5.4	1070	156	13	52	3	69	2.5	22.5	86	0.01
KL40-07	383.7	386.7	2.75	27500	2.4	8.4	253	53	14	69	4	93	1.5	34.0	109	0.01
KL40-07	386.7	389.7	3.15	31500	2.2	6.6	79	50	7	70	4	62	1.4	37.5	110	0.01
KL40-07	389.7	392.7	2.36	23600	1.34	4.8	940	298	50	151	3	53	5.2	37.5	157	0.01
KL40-07	392.7	395.7	4.53	45300	2.72	5.7	206	72	11	16	3	47	2	30.0	81	0.01
KL40-07	395.7	398.7	3.51	35100	2.42	7.2	108	32	5	18	3	54	1.6	7.5	87	0.01
KL40-07	398.7	401.7	2.72	27200	1.68	5.1	1100	365	29	12	3	47	1.3	19.5	111	0.01
KL40-07	401.7	404.7	1.96	19600	1.86	6.3	490	129	31	96	5	36	0.9	31.0	197	3.36
KL40-07	404.7	407.7	1.52	15200	1.28	2.2	830	212	13	22	2	38	0.7	26.0	126	0.01
KL40-07	407.7	410.7	2.34	23400	1.54	5.6	480	109	13	16	4	46	0.9	34.0	84	0.01
KL40-07	410.7	413.7	1.21	12100	0.72	6.3	91	41	7	27	5	50	0.9	12.0	103	0.01
KL40-07	413.7	416.7	2.45	24500	1.64	23.5	96	37	7	32	4	34	0.7	21.0	83	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL40-07	416.7	419.7	3.01	30100	1.55	12.4	790	730	12	29	5	37	1.3	22.5	37	0.01
KL40-07	419.7	422.7	2.38	23800	1.22	6.4	610	119	11	26	6	43	0.8	23.5	73	0.01
KL40-07	422.7	425.7	2.18	21800	0.94	4.3	600	64	4	71	6	40	0.4	6.0	44	0.01
KL40-07	425.7	428.7	2.6	26000	1.4	8.3	690	297	8	18	8	47	0.7	23.5	55	0.01
KL40-07	428.7	431.7	3.7	37000	1.6	8.6	720	67	5	12	20	49	0.5	16.0	112	0.01
KL40-07	431.7	434.7	2.84	28400	1.36	8.4	840	242	10	8	6	22	0.9	17.5	52	0.01
KL40-07	434.7	437.7	3.09	30900	2.55	23	6010	2310	81	14	7	28	2.8	16.0	138	0.01
KL40-07	437.7	440.7	0.8	8000	2.68	28.3	7010	1750	320	396	15	22	11.5	21.5	183	0.44
KL40-07	440.7	443.7	0.59	5900	0.84	9.8	1040	235	42	2100	5	15	1.6	12.0	153	0.12
KL40-07	443.7	446.7	0.314	3140	0.68	3.8	430	120	26	70	2	8	5.1	8.4	166	0.01
KL40-07	446.7	449.7	0.136	1360	0.35	1.4	289	77	21	159	2	9	0.9	7.3	102	0.01
KL40-07	449.7	452.7	0.136	1360	0.26	1.1	324	161	19	105	1	6	0.8	7.0	124	0.01
KL40-07	452.7	455.7	0.17	1700	0.32	2.6	460	1020	48	289	3	14	0.9	13.8	116	0.01
KL40-07	455.7	458.7	0.181	1810	0.28	1.2	440	820	30	110	1	8	0.5	7.0	108	0.01
KL40-07	458.7	461.7	0.195	1950	0.22	2.6	241	368	42	170	1	15	0.6	14.6	158	0.01
KL40-07	461.7	464.7	0.144	1440	0.3	2.3	750	2120	100	155	2	26	3	13.3	89	0.01
KL40-07	464.7	467.7	0.081	810	0.46	2.1	520	530	28	284	1	9	4.8	7.0	81	0.1
KL40-07	467.7	470.7	0.1	1000	0.34	1.2	319	1300	26	123	1	11	0.01	9.5	105	0.01
KL40-07	470.7	472.9	0.094	940	1.4	3.7	500	650	220	156	1	8	0.4	5.3	139	0.1
KL40-07	472.9	474.5	0.0247	247	0.3	1.4	510	590	24	211	1	10	1	8.5	118	0.01
KL40-07	474.5	476.6	0.459	4590	0.33	1.6	1070	2060	40	75	2	18	0.4	18.5	135	0.01
KL40-07	476.6	479.1	1.31	13100	2.14	7.5	1190	1420	54	789	42	24	0.4	20.0	128	0.01
KL40-07	479.1	482.2	2.36	23600	2.56	14.4	720	630	42	68	7	25	0.4	21.5	155	0.01
KL40-07	482.2	485.3	2.35	23500	1.74	25.8	530	125	45	23	45	28	0.8	24.0	96	0.01
KL40-07	485.3	488.4	2.26	22600	2.02	23.5	440	120	38	33	63	27	1.1	25.5	127	0.01
KL40-07	488.4	491.5	3.27	32700	3.34	25.1	4070	1960	50	46	65	58	1	31.0	49	0.01
KL40-07	491.5	494.7	1.67	16700	2.28	9.3	960	132	41	25	31	58	1.8	30.0	67	0.01
KL40-07	494.7	497.7	2.56	25600	2.34	14.7	2720	540	36	71	8	31	1.1	21.0	72	0.01
KL40-07	497.7	500.7	2.16	21600	1.83	7.4	1240	315	29	27	4	50	1.2	20.0	52	0.01
KL40-07	500.7	503.7	2.71	27100	2.24	4.8	540	510	24	9	5	54	1.3	18.0	64	0.01
KL40-07	503.7	506.7	3.49	34900	3.68	6.2	358	325	15	5	5	142	1.6	22.5	51	0.01
KL40-07	506.7	509.7	3.13	31300	2.58	2	221	86	6	10	4	36	1.1	6.0	40	0.01
KL40-07	509.7	512.7	3.26	32600	2.74	2.3	251	47	2	7	1	39	0.8	8.0	41	0.01
KL40-07	512.7	515.7	2.77	27700	2.9	1.7	221	115	7	8	3	40	1.8	11.5	58	0.01
KL40-07	515.7	518.7	3.59	35900	3.1	2.6	440	31	4	7	1	36	0.7	7.0	55	0.01
KL40-07	518.7	521.7	1.94	19400	1.78	2	470	186	1	2	3	31	0.4	5.0	45	0.01
KL40-07	521.7	524.7	3.25	32500	3.04	4.6	1340	1080	0.01	2	1	54	0.3	7.5	32	0.01
KL40-07	524.7	527.7	3.15	31500	2.8	3.8	1260	1650	0.01	5	4	53	0.5	5.0	39	0.01
KL40-07	527.7	530.7	3.19	31900	3.26	5.3	1070	410	9	21	3	56	0.9	6.0	64	0.01
KL40-07	530.7	533.7	3.29	32900	3.1	6.7	600	48	3	5	3	49	0.6	19.0	47	0.01
KL40-07	533.7	536.7	3.32	33200	2.92	5.4	790	86	2	10	3	53	0.4	12.0	40	0.01
KL40-07	536.7	539.7	2.82	28200	2.58	6.2	570	72	1	7	4	44	0.5	12.0	36	0.01
KL40-07	539.7	542.7	4.28	42800	5.3	10.2	1180	271	4	5	3	67	0.6	30.0	34	0.01
KL40-07	542.7	545.3	2.9	29000	3.15	5.4	600	42	2	4	4	59	0.3	5.0	36	0.01
KL40-07	545.3	547.1	2.11	21100	2.4	4	570	16	21	11	4	96	7.9	8.0	40	0.01
KL40-07	547.1	548.9														
KL40-07	548.9	551.4	0.6	6000	0.72	8.8	4150	3470	49	4	25	27	1.5	16.0	33	0.01
KL40-07	551.4	554.2	0.88	8800	1.01	7.1	680	435	25	12	24	48	1.7	6.0	28	0.01
KL40-07	554.2	555.2	2.2	22000	2.56	20.1	1500	500	10	2	64	41	1.7	8.0	43	0.01
KL40-07	555.2	557.7	0.413	4130	0.32	4.1	1050	640	8	4	14	6	0.4	10.5	26	0.01
KL40-07	557.7	560.7	0.078	780	1.11	1.8	2300	810	50	16	12	2	0.7	4.3	23	0.01
KL40-07	560.7	563.7	0.407	4070	0.67	90	23000	26700	66	189	268	8	1.8	73.5	34	0.01
KL40-07	563.7	566.7	0.078	780	0.13	3.5	2610	1540	6	77	16	3	0.01	9.0	17	0.01
KL40-07	566.7	569.7	0.049	490	0.08	0.7	5140	1490	6	7	3	2	0.01	10.3	22	0.01
KL40-07	569.7	572.7	0.12	1200	0.21	1.8	2020	440	20	41	36	5	0.2	8.3	19	0.01
KL40-07	572.7	575.7	0.127	1270	0.22	2.1	2050	430	21	41	32	4	0.4	7.0	18	0.01
KL40-07	575.7	578.7	0.24	2400	0.39	2.6	520	57	17	77	12	5	0.7	5.5	26	0.01
KL40-07	578.7	581.7	0.166	1660	0.28	1.8	1230	240	22	122	26	4	0.3	5.8	21	0.01
KL40-07	581.7	584.7	0.167	1670	0.27	1.9	1440	260	25	107	32	4	0.3	8.7	19	0.01
KL40-07	584.7	587.7	0.245	2450	0.37	3	530	97	27	133	23	2	0.7	8.2	18	0.01
KL40-07	587.7	590.7	0.68	6800	1.07	5.7	690	41	40	93	10	6	0.4	8.1	16	0.1
KL40-07	590.7	593.7	0.67	6700	1.08	5.7	700	48	35	90	9	5	0.7	9.0	15	0.01
KL40-07	593.7	596.7	0.4	4000	0.6	4.3	10400	168	31	26	6	17	1	11.5	20	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL40-07	596.7	599.7	0.41	4100	0.64	4.5	10200	156	28	30	6	16	0.7	10.3	21	0.01
KL40-07	599.7	602.7	0.402	4020	0.84	4.3	3400	359	130	100	5	4	0.8	11.0	16	0.1
KL40-07	602.7	605.7	0.421	4210	0.81	4.3	3600	368	130	102	5	5	1	10.6	16	0.1
KL40-07	605.7	608.7	1.04	10400	1.43	6.7	780	118	28	240	4	14	1	13.3	27	0.01
KL40-07	608.7	611.7	1.03	10300	1.51	6.9	760	110	31	236	3	16	1.1	13.5	29	0.01
KL40-07	611.7	614.7	0.23	2300	0.4	2.1	580	64	26	71	11	3	1.1	19.5	22	0.01
KL40-07	614.7	617.7	0.044	440	0.04	0.6	331	106	12	16	5	2	0.7	6.0	17	0.01
KL40-07	617.7	620.7	0.044	440	0.04	0.6	350	105	14	14	6	1	1	4.5	17	0.01
KL40-07	620.7	623.7	0.118	1180	0.12	1	347	130	12	18	1	3	0.5	2.5	24	0.01
KL40-07	623.7	626.7	0.121	1210	0.1	0.8	356	123	12	17	1	5	0.8	3.0	24	0.01
KL40-07	626.7	629.7	0.254	2540	0.35	3	460	104	38	127	24	3	0.8	8.6	19	0.01
KL40-07	629.7	632.7	0.095	950	0.08	1.8	610	460	34	4	9	2	1.6	7.5	19	0.01
KL40-07	632.7	635.7	0.097	970	0.09	1.7	620	460	32	3	9	4	1.7	6.0	20	0.01
KL40-07	635.7	638.7	0.458	4580	0.07	2.6	440	140	56	23	34	2	3	7.8	20	0.01
KL40-07	638.7	641.7	0.27	2700	0.27	1.4	430	67	29	6	4	4	0.4	5.3	22	0.01
KL40-07	641.7	644.7	0.261	2610	0.26	1.4	420	65	26	7	3	4	0.4	5.5	26	0.01
KL40-07	644.7	647.7	0.389	3890	0.07	2.4	450	148	52	22	32	3	2.5	11.3	19	0.01
KL40-07	647.7	650.7	0.077	770	0.05	0.6	191	21	12	4	1	2	0.01	3.3	21	0.01
KL40-07	650.7	653.7	0.241	2410	0.28	1.6	336	19	23	3	1	7	0.2	13.3	16	0.01
KL40-07	653.7	656.7	0.23	2300	0.3	1.8	334	21	25	3	2	4	0.01	14.3	17	0.01
KL40-07	656.7	659.7	0.26	2600	0.38	1.5	228	17	10	7	3	7	0.2	6.9	18	0.01
KL40-07	659.7	662.7	0.26	2600	0.39	1.8	232	19	12	6	4	9	0.2	4.3	18	0.01
KL40-07	662.7	665.7	0.67	6700	0.61	3.9	160	14	13	13	5	15	0.7	15.7	27	0.01
KL40-07	665.7	668.7	0.69	6900	0.49	4.1	262	16	33	12	3	16	1.4	7.8	8	0.01
KL40-07	668.7	671.7	0.7	7000	0.58	4.1	265	17	30	12	4	20	1.4	9.8	10	0.01
KL40-07	671.7	674.7	0.22	2200	0.21	1.4	211	15	23	4	0.01	1	0.6	4.5	23	0.01
KL40-07	674.7	677.7	0.66	6600	0.56	2.7	178	13	23	4	1	15	1	9.5	23	0.01
KL40-07	677.7	680.7	0.69	6900	0.56	2.9	182	15	20	5	1	12	0.5	9.3	22	0.01
KL40-07	680.7	683.7	0.459	4590	0.33	2.4	232	20	25	14	7	8	1.2	14.9	37	0.01
KL40-07	683.7	686.2	0.509	5090	0.4	1.2	75	12	15	18	1	12	1.2	10.0	20	0.01
KL40-07	686.2	689.2	0.505	5050	0.41	1.3	76	13	13	15	0.01	12	0.9	9.0	20	0.01
KL40-07	689.2	692.3	0.499	4990	0.53	1.6	218	80	7	116	2	11	0.01	7.0	38	0.01
KL40-07	692.3	695.4	0.435	4350	0.3	1.6	74	18	30	14	1	13	0.3	9.5	33	0.01
KL40-07	695.4	696.2	0.271	2710	0.06	1.2	55	8	3	19	1	7	0.01	4.8	17	0.01
KL40-07	696.2	698.6	0.434	4340	0.29	1.7	69	18	27	13	1	12	0.01	10.8	32	0.01
KL40-07	698.6	701.6	1.75	17500	1.28	4.8	76	11	6	11	10	16	0.8	10.0	60	0.01
KL40-07	701.6	704.6	1.49	14900	1.37	1.7	89	13	5	12	0.01	15	0.01	15.0	60	0.01
KL40-07	704.6	707.3	1.07	10700	0.89	1.8	78	10	4	6	0.01	12	0.01	9.3	51	0.01
KL40-07	707.3	710.4	0.504	5040	0.46	1.1	61	7	4	23	0.01	10	0.01	4.5	30	0.01
KL40-07	710.4	713.6	0.59	5900	0.81	2	122	10	2	92	0.01	10	0.01	5.3	21	0.01
KL40-07	713.6	716.6	0.63	6300	0.81	1.9	126	12	2	82	0.01	9	0.01	6.5	20	0.01
KL40-07	716.6	719.6	0.379	3790	0.39	1.8	61	11	2	119	2	6	0.01	4.3	16	0.01
KL40-07	719.6	722.6	0.387	3870	0.39	1.6	62	11	2	122	2	6	0.01	4.0	17	0.01
KL40-07	722.6	725.6	0.282	2820	0.07	1.6	58	10	1	20	2	6	0.01	6.3	19	0.01
KL40-07	725.6	728.6	0.529	5290	0.17	1.6	48	10	2	35	0.01	8	0.01	6.5	45	0.01
KL40-07	728.6	731.6	0.398	3980	0.23	0.9	65	15	5	93	0.01	11	0.01	8.5	36	0.01
KL40-07	731.6	734.6	0.496	4960	0.3	1.6	50	10	1	80	0.01	9	0.01	8.0	34	0.01
KL40-07	734.6	737.6	0.352	3520	0.23	0.9	38	9	1	67	0.01	10	0.01	6.3	38	0.01
KL40-07	737.6	740.6	0.362	3620	0.22	0.9	56	12	3	147	0.01	9	0.01	13.4	39	0.01
KL40-07	740.6	743.6	0.263	2630	0.21	0.6	64	19	1	10	0.01	5	0.01	4.0	28	0.01
KL40-07	743.6	746.6	0.242	2420	0.16	0.8	45	15	1	129	0.01	6	0.01	3.8	25	0.01
KL40-07	746.6	749.6	0.459	4590	0.38	1.2	90	48	7	8	0.01	5	0.01	4.5	29	0.01
KL40-07	749.6	752.6	0.58	5800	0.5	1.9	315	35	17	35	1	5	0.01	5.3	45	0.21
KL40-07	752.6	755.6	0.342	3420	0.14	1.3	68	18	4	121	1	6	0.01	7.0	43	0.01
KL40-07	755.6	758.6	0.351	3510	0.29	1.1	67	22	6	27	0.01	7	0.01	5.0	48	0.01
KL40-07	758.6	761.6	0.359	3590	0.14	1	247	87	3	566	0.01	8	0.01	7.8	41	0.01
KL40-07	761.6	764.6	0.521	5210	0.29	1.6	330	130	1	50	1	7	0.01	5.8	39	0.01
KL40-07	764.6	767.2	0.091	910	0.01	1.1	59	25	2	30	0.01	6	0.01	4.0	48	0.01
KL40-07	767.2	769.6	0.071	710	0.01	0.1	58	21	2	73	0.01	4	0.2	1.2	115	0.01
KL40-07	769.6	771.8	0.064	640	0.03	0.1	70	31	23	84	0.01	5	0.2	3.6	110	0.01
KL40-07	771.8	773.6	0.228	2280	0.15	1.5	74	34	29	20	3	11	0.6	6.8	72	0.01
KL40-07	773.6	776.6	0.327	3270	0.32	2.6	280	385	42	30	4	12	1.4	11.3	48	0.01
KL40-07	776.6	777.5	0.201	2010	0.03	1.8	264	142	25	62	2	5	0.8	4.5	144	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL40-07	777.5	779.6	0.298	2980	0.04	2.5	278	145	45	203	3	10	2	8.0	136	0.01
KL40-07	779.6	782.6	0.346	3460	0.03	3.2	250	107	37	96	3	11	0.9	5.8	50	0.01
KL40-07	782.6	785.6	0.57	5700	0.07	2.6	117	54	7	289	1	8	0.4	10.5	238	0.01
KL40-07	785.6	788.6	0.374	3740	0.02	2.1	187	92	30	101	1	6	0.8	4.5	114	0.01
KL40-07	788.6	791.1	0.8	8000	0.11	8.2	770	510	400	76	5	5	11.6	4.5	201	2.3
KL40-07	791.1	794.3	0.257	2570	0.06	1.5	141	83	13	205	0.01	7	0.5	4.8	72	0.14
KL40-07	794.3	797.4	0.92	9200	0.07	5.4	560	240	630	365	4	9	5.1	8.5	110	0.37
KL40-07	797.4	799.2	1.04	10400	0.17	8.8	5200	2700	1100	930	0.01	16	19.4	18.8	89	1.34
KL40-07	799.2	800.4	0.69	6900	0.11	3.5	3100	1300	150	143	1	9	3.8	6.5	114	0.46
KL40-07	800.4	803.6	0.197	1970	0.04	1.3	440	94	29	157	0.01	8	0.6	3.0	39	0.01
KL40-07	803.6	806.6	0.209	2090	0.02	1.8	85	48	18	24	1	6	0.4	4.3	205	0.01
KL40-07	806.6	809.6	0.098	980	0.01	0.5	30	8	1	97	0.01	1	0.01	3.6	10	0.01
KL40-07	809.6	812.6	0.385	3850	0.09	1.3	220	138	15	51	0.01	8	0.3	4.5	22	0.01
KL40-07	812.6	815.6	0.332	3320	0.15	0.9	85	28	3	28	0.01	23	0.01	7.0	35	0.01
KL40-07	815.6	818.6	0.298	2980	0.09	1	49	9	0.01	246	0.01	10	0.01	4.3	21	0.01
KL40-07	818.6	821.6	0.291	2910	0.1	1	46	11	2	253	0.01	10	0.01	4.0	22	0.01
KL40-07	821.6	824.6	0.425	4250	0.17	1.1	72	13	2	206	0.01	18	0.01	6.5	14	0.01
KL40-07	824.6	827.6	0.443	4430	0.17	1	74	12	2	193	0.01	15	0.01	7.0	13	0.01
KL40-07	827.6	829.6	1.42	14200	0.51	3.9	209	6	8	18	1	29	0.4	12.5	30	0.01
KL40-07	829.6	832.6	1.52	15200	0.67	4.3	187	6	7	15	1	37	0.01	12.0	30	0.01
KL40-07	832.6	835.2	0.6	6000	0.39	2	167	1	5	11	3	34	0.4	5.5	35	0.01
KL40-07	835.2	836.5	0.625	6250	0.37	2.3	165	6	5	11	2	37	0.3	5.3	35	0.01
KL40-07	836.5	839.6	0.448	4480	0.35	2.2	275	75	21	93	3	12	4.4	5.8	23	0.11
KL40-07	839.6	842.6	1.46	14600	0.63	3.9	190	6	11	16	1	24	0.4	12.5	42	0.01
KL40-07	842.6	845.6	0.124	1240	0.08	0.8	263	8	6	13	1	5	0.2	3.3	24	0.01
KL40-07	845.6	848.6	0.62	6200	0.34	4.6	287	5	8	20	2	13	0.2	8.0	26	0.01
KL40-07	848.6	851.6	0.61	6100	0.34	4.2	272	5	7	19	2	15	0.3	8.3	27	0.01
KL40-07	851.6	854.6	1.45	14500	0.65	4.2	177	6	8	16	1	36	0.01	12.8	32	0.01
KL40-07	854.6	857.6	0.84	8400	0.39	1.9	138	24	20	57	1	21	0.01	9.0	50	0.01
KL40-07	857.6	860.6	0.74	7400	0.33	2.1	195	10	33	196	1	17	0.8	10.0	35	0.01
KL40-07	860.6	863.6	0.72	7200	0.37	2.3	199	17	37	213	1	17	0.7	9.5	32	0.01
KL40-07	863.6	866.6	1.5	15000	0.54	4	205	6	5	18	1	28	0.01	9.5	28	0.01
KL40-07	866.6	869.6	0.47	4700	0.26	3.5	272	7	10	34	2	8	0.01	8.3	15	0.01
KL40-07	869.6	872.6	0.46	4600	0.28	3.2	287	7	12	28	1	8	0.01	6.3	15	0.01
KL40-07	872.6	875.6	0.25	2500	0.2	1.7	207	6	8	14	1	4	0.5	4.8	21	0.01
KL40-07	875.6	878.6	0.24	2400	0.14	1.9	206	6	6	12	4	4	0.01	4.0	15	0.01
KL40-07	878.6	881.6	0.6	6000	0.38	4	650	10	21	20	5	14	0.01	5.0	26	0.01
KL40-07	881.6	884.6	0.173	1730	0.12	1.5	201	17	14	23	1	6	0.01	5.2	18	0.01
KL40-07	884.6	887.6	0.433	4330	0.34	2	323	68	26	95	3	15	3.6	3.8	23	0.01
KL40-07	887.6	890.6	0.088	880	0.07	0.8	123	6	5	16	1	4	0.2	2.5	17	0.01
KL40-07	890.6	893.6	0.127	1270	0.07	0.8	235	8	6	13	1	5	0.3	2.8	23	0.01
KL40-07	893.6	896.6	0.088	880	0.07	0.8	108	7	5	17	1	3	0.2	2.5	20	0.01
KL40-07	896.6	899.6	0.22	2200	0.1	1.5	358	42	11	14	1	2	0.4	3.3	15	0.01
KL40-07	899.6	902.3	0.226	2260	0.1	1.4	344	43	11	12	1	4	0.3	3.5	14	0.01
KL40-07	902.3	904.3	0.085	850	0.05	1.3	113	19	35	15	1	2	0.7	2.5	13	0.01
KL40-07	904.3	907.4	0.086	860	0.02	0.6	120	26	12	13	1	2	0.5	2.3	12	0.01
KL40-07	907.4	909.6	0.072	720	0.03	0.6	231	12	8	14	5	2	0.6	3.0	18	0.01
KL40-08	0	2.7	0.0024	24	0.04	0.1	690	143	13	6	0.01	1	4.6	1.5	18	0.01
KL40-08	2.7	5.7	0.0011	11	0.01	0.1	317	128	8	6	0.01	1	3.5	1.5	19	0.01
KL40-08	5.7	8.7	0.0027	27	0.05	1	530	162	19	6	0.01	1	10.4	1.8	18	0.1
KL40-08	8.7	11.7	0.0026	26	0.18	1.9	660	231	34	7	5	1	7.6	2.5	23	0.4
KL40-08	11.7	14.7	0.0084	84	0.26	2.1	1820	1000	47	3	4	1	22	6.0	21	0.28
KL40-08	14.7	17.7	0.0167	167	0.06	2.1	560	540	39	4	1	1	52	3.8	17	0.16
KL40-08	17.7	20.7	0.0048	48	0.05	1.2	710	450	32	9	2	1	9.7	1.0	18	0.1
KL40-08	20.7	23.7	0.0077	77	0.24	3.7	1130	920	110	31	14	2	8.2	2.3	30	0.22
KL40-08	23.7	26.7	0.0048	48	0.02	1.2	343	253	56	21	10	1	3	1.5	25	0.01
KL40-08	26.7	29.7	0.0047	47	0.08	0.1	175	65	66	11	4	1	8.5	0.0	32	0.01
KL40-08	29.7	32.7	0.0081	81	0.07	1.6	400	159	67	19	7	2	24	0.5	30	0.12
KL40-08	32.7	35.7	0.0246	246	0.29	2.5	303	215	120	82	27	1	24	2.1	58	0.16
KL40-08	35.7	38.7	0.0058	58	0.05	0.8	373	106	38	14	4	1	6.5	0.8	34	0.1
KL40-08	38.7	41.7	0.0142	142	0.04	0.1	147	68	48	16	6	1	4.6	0.8	30	0.1
KL40-08	41.7	44.7	0.0129	129	1.87	3.2	1030	740	120	14	2	2	20.3	2.5	26	0.26
KL40-08	44.7	47.7	0.0037	37	0.08	0.7	276	143	50	9	1	1	6.5	0.8	23	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL40-08	47.7	50.7	0.0014	14	0.08	0.7	314	97	36	7	0.01	2	7.5	1.3	27	0.01
KL40-08	50.7	53.7	0.0056	56	0.18	2	3600	690	50	19	30	2	37.8	2.8	30	1.2
KL40-08	53.7	56.7	0.005	50	0.1	1.2	480	142	67	11	3	3	5.8	1.5	29	0.12
KL40-08	56.7	59.7	0.0052	52	0.05	0.1	230	112	50	24	6	2	4.6	1.3	29	0.01
KL40-08	59.7	62.7	0.0046	46	0.04	1.4	450	580	30	7	1	1	15.8	1.7	21	0.11
KL40-08	62.7	65.7	0.0084	84	0.05	0.9	460	420	39	16	0.01	1	10.5	1.3	24	0.01
KL40-08	65.7	68.7	0.0045	45	0.08	0.9	570	308	41	7	3	2	24	1.3	24	0.01
KL40-08	68.7	71.7	0.0025	25	0.1	2.2	750	341	37	7	0.01	1	7.9	3.5	24	0.01
KL40-08	71.7	74.7	0.049	490	0.15	13.4	3400	3070	190	4	0.01	1	52	32.0	23	0.1
KL40-08	74.7	77.7	0.0367	367	0.16	8.6	2825	1800	150	25	1	3	42	21.3	25	0.18
KL40-08	77.7	80.7	0.0096	96	0.31	1.4	840	460	150	20	6	2	13.8	4.3	35	0.14
KL40-08	80.7	83.7	0.0043	43	0.9	1.8	5200	900	64	7	4	1	12.6	6.0	36	0.16
KL40-08	83.7	86.7	0.05	500	0.23	12.1	13000	2400	69	24	77	12	40	157.0	44	0.16
KL40-08	86.7	89.7	0.054	540	0.25	13.4	13300	2500	76	23	75	10	32	145.0	43	0.1
KL40-08	89.7	92.7	0.0201	201	0.18	5	1550	1210	76	650	49	4	4.6	7.8	25	0.01
KL40-08	92.7	95.7	0.081	810	0.09	3.1	760	235	75	980	73	5	7.3	10.0	65	0.01
KL40-08	95.7	96.5	0.111	1110	0.21	2.3	148	121	660	1400	71	3	11.8	4.8	61	0.01
KL40-08	96.5	97.8	0.0199	199	0.05	0.8	130	46	31	420	4	3	6.1	1.5	29	0.01
KL40-08	97.8	99.9	0.047	470	0.1	1.2	309	70	48	50	5	10	16.4	2.0	16	0.01
KL40-08	99.9	102.8	0.054	540	0.12	0.9	153	51	29	114	3	7	2.6	2.5	21	0.41
KL40-08	102.8	103.7	0.464	4640	0.77	5.2	580	216	390	1410	10	2	180	6.0	81	0.65
KL40-08	103.7	105.9	2.18	21800	0.75	3.6	1260	400	670	377	4	5	310	12.0	136	1
KL40-08	105.9	107.7	2.89	28900	1.16	3.7	1490	1400	380	1200	3	5	120	4.5	79	0.47
KL40-08	107.7	110.4	1.83	18300	1	2.1	283	136	280	460	5	3	160	4.2	150	0.54
KL40-08	110.4	112.4	0.218	2180	0.97	13.7	32700	7500	500	87	6	6	40	6.0	61	0.68
KL40-08	112.4	114.9	0.453	4530	0.82	5.7	660	227	440	1280	10	3	190	6.8	89	0.68
KL40-08	114.9	117.5	0.056	560	0.68	4.2	212	129	160	670	8	1	16	7.8	108	0.23
KL40-08	117.5	119.1	0.066	660	0.89	7.2	5100	5600	220	455	6	3	12	8.0	81	0.2
KL40-08	119.1	122.1	0.456	4560	2.15	33.4	670	176	300	490	160	1	30	8.0	208	0.58
KL40-08	122.1	124.8	0.044	440	2.92	87	14800	28200	520	680	12	1	50	19.0	161	2.88
KL40-08	124.8	126.7	0.0126	126	0.19	6.4	4000	5700	150	56	5	1	4.8	10.3	46	0.01
KL40-08	126.7	128.7	0.0324	324	4.05	56	45700	8900	570	1380	16	5	40	19.5	161	2.93
KL40-08	128.7	131.7	0.153	1530	2.8	300	72000	41500	450	87	27	7	100	18.5	96	39.8
KL40-08	131.7	134.7	1.05	10500	2.31	300	83000	60200	1850	90	32	8	50	14.5	73	29.2
KL40-08	134.7	137.6	0.159	1590	2.47	13.6	15300	4300	510	206	6	5	29.8	13.5	32	1.72
KL40-08	137.6	140.4	0.33	3300	1.82	12.6	14400	2900	1160	120	8	9	53	15.0	49	1.3
KL40-08	140.4	142.1	0.0264	264	0.48	1.6	4900	800	78	126	0.01	3	2.5	4.5	25	0.26
KL40-08	142.1	145	0.076	760	1.33	8.3	4100	2540	340	368	1	4	18.8	7.0	39	0.5
KL40-08	145	146.7	0.21	2100	1.68	6.3	9300	4300	770	134	3	12	25.8	10.8	46	0.43
KL40-08	146.7	148.4	0.043	430	0.26	4.5	6100	2200	61	24	20	4	3.4	13.5	31	0.16
KL40-08	148.4	151.2	0.0094	94	0.17	3	2450	890	28	42	11	2	1.5	4.3	27	0.24
KL40-08	151.2	153.9	0.005	50	0.15	1.7	1130	313	18	23	9	1	1.8	2.6	31	0.18
KL40-08	153.9	156.4	0.0041	41	0.37	2	1150	470	23	22	8	2	3.5	3.5	27	0.1
KL40-08	156.4	158.7	0.0087	87	0.24	5.1	8700	2200	38	14	14	1	14.3	8.5	27	0.38
KL40-08	158.7	160.9	0.0056	56	0.18	2.1	2010	1250	31	37	6	1	4.9	3.0	29	0.16
KL40-08	160.9	163.7	0.32	3200	1.5	17.7	15000	5300	1480	192	24	9	53	12.5	48	2.85
KL40-08	163.7	166.6	0.0166	166	0.21	4	2520	790	45	57	14	2	2.5	2.8	31	0.13
KL40-08	166.6	169.8	0.096	960	0.4	22.2	11500	5600	230	166	46	3	22	14.0	21	0.64
KL40-08	169.8	172.8	0.0169	169	0.18	5.7	1980	1150	110	620	56	3	5.5	15.1	28	0.01
KL40-08	172.8	175.9	0.149	1490	0.41	25.6	20800	7500	220	156	45	17	12.3	24.5	20	0.4
KL40-08	175.9	178.6	0.092	920	0.4	18.7	11500	5100	240	152	36	4	30.5	15.0	21	0.6
KL40-08	178.6	180.2	0.091	910	0.37	19.9	12800	5700	190	100	36	7	16	25.5	19	0.37
KL40-08	180.2	182.4	0.0297	297	0.4	14.2	7300	3600	93	29	25	2	9.5	16.8	18	0.2
KL40-08	182.4	185.5	0.35	3500	2.07	12.1	13100	2500	490	329	47	16	10.3	31.5	43	0.45
KL40-08	185.5	188.6	0.53	5300	2.4	17.3	60500	3300	570	322	50	49	14.8	47.7	61	0.34
KL40-08	188.6	190.2	1.27	12700	2.26	45	86500	12900	800	345	160	50	23.6	86.5	99	0.49
KL40-08	190.2	192.6	1.89	18900	1.78	14.5	4900	740	1320	1520	48	57	14.8	84.0	68	0.24
KL40-08	192.6	195.6	2.65	26500	1.6	13.5	2900	1210	2600	1230	9	75	7.4	52.0	54	0.28
KL40-08	195.6	197.7	1.54	15400	1.3	5.7	1900	550	2560	3050	140	64	7.2	49.2	70	0.25
KL40-08	197.7	200.7	1.59	15900	1.12	8.7	1260	340	1970	910	33	89	24.7	39.0	73	0.26
KL40-08	200.7	203	1.48	14800	1.1	12.7	4600	740	2640	420	44	60	23.7	98.0	44	0.35
KL40-08	203	205.5	1.94	19400	1.78	33.7	31000	4700	2500	245	66	74	18.3	29.0	64	0.36
KL40-08	205.5	207.2	0.73	7300	1.2	39	47100	17200	8200	259	75	25	16	37.0	45	0.55

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL40-08	207.2	209.7	0.54	5400	1.1	54	40600	39300	5900	321	100	19	30	63.0	75	0.35
KL40-08	209.7	212.7	0.058	580	0.25	14.2	8500	8900	280	75	31	5	5	27.0	36	0.1
KL40-08	212.7	215.3	0.0312	312	0.17	4	2300	3600	160	46	4	1	3.6	11.3	32	0.01
KL40-08	215.3	216.5	0.142	1420	0.31	6	7000	4100	140	101	13	3	4.7	17.8	47	0.01
KL40-08	216.5	218.7	0.085	850	0.25	5.6	6100	6000	270	126	7	2	5.7	14.9	24	0.01
KL40-08	218.7	221.7	0.0097	97	0.3	4	4500	3670	94	26	5	1	4.3	10.0	23	0.01
KL40-08	221.7	224.1	0.0209	209	0.28	7	8100	7600	130	18	10	2	6.5	6.5	25	0.12
KL40-08	224.1	225.9	0.0093	93	0.27	3.9	4800	5400	53	26	2	1	6.7	2.5	24	0.1
KL40-08	225.9	227.7	0.0216	216	0.35	10.2	8600	8100	150	30	9	1	8	12.1	23	0.16
KL40-08	227.7	230.7	0.0224	224	0.41	6.4	5500	6700	180	123	22	1	10	10.3	28	0.11
KL40-08	230.7	233.7	0.0251	251	0.33	14	12000	16300	330	51	5	3	15.4	17.0	27	0.16
KL40-08	233.7	235.9	0.073	730	0.35	26.5	32500	38700	550	168	4	1	36	9.5	25	0.16
KL40-08	235.9	238	0.0169	169	3.27	94	27500	26600	540	1720	10	1	36	12.0	90	4.48
KL40-08	238	239.7	0.0254	254	0.36	10.2	8300	8000	180	47	5	1	8.2	17.5	30	0.1
KL40-08	239.7	242.7	0.0167	167	0.23	8.6	5200	5200	140	70	3	2	8.1	20.3	24	0.14
KL40-08	242.7	245.7	0.04	400	0.43	20.4	22600	12300	160	100	24	1	11	28.5	29	0.21
KL40-08	245.7	248.7	0.0181	181	0.32	8.9	8500	5300	90	82	6	4	4.5	17.8	19	0.1
KL40-08	248.7	251.7	0.037	370	0.45	19.9	19300	16800	110	108	6	2	17.8	26.0	28	0.15
KL40-08	251.7	254.7	0.0192	192	0.46	6.6	4600	2480	110	35	2	2	4	14.5	25	0.11
KL40-08	254.7	257.7	0.037	370	0.41	10.2	9100	5600	94	137	25	3	8.1	15.5	24	0.15
KL40-08	257.7	260.3	0.0231	231	0.27	7.5	6500	3300	74	138	8	2	4	12.0	22	0.11
KL40-08	260.3	263.4	0.035	350	0.44	12.1	11600	7000	84	189	24	3	8.2	20.3	26	0.13
KL40-08	263.4	266.3	0.059	590	2.92	17.9	24400	7800	480	59	6	12	14	12.1	41	0.11
KL40-08	266.3	269.7	0.063	630	0.78	10.5	11100	4600	290	95	14	7	8.1	10.5	27	0.14
KL40-08	269.7	272.4	0.093	930	0.31	8.2	6400	4800	380	25	5	5	4.8	9.5	21	0.11
KL40-08	272.4	275.6	0.064	640	0.34	2.9	4600	1040	230	96	10	4	2.9	10.0	32	0.11
KL40-08	275.6	278.7	0.144	1440	0.62	3.1	13000	1070	280	340	26	9	8.5	31.3	58	0.23
KL40-08	278.7	281.7	0.0342	342	0.17	5.7	1920	1330	130	33	1	2	28	22.2	22	0.12
KL40-08	281.7	284.7	2.51	25100	3.44	18.8	3600	258	310	148	62	25	2.5	19.2	35	0.2
KL40-08	284.7	287.7	0.0328	328	0.31	0.9	384	76	63	77	3	3	3.5	4.0	21	0.1
KL40-08	287.7	290.7	0.0121	121	0.58	0.9	410	161	68	93	5	1	14.5	10.3	26	0.14
KL40-08	290.7	293.7	0.0069	69	0.54	2.5	354	370	460	8	0.01	2	12	6.0	18	0.14
KL40-08	293.7	296.7	0.0123	123	0.56	1.4	410	281	240	50	4	1	15.9	8.0	21	0.17
KL40-08	296.7	299.7	0.0038	38	0.15	0.9	114	56	130	16	0.01	3	2.3	6.3	45	0.01
KL40-08	299.7	302.7	0.0035	35	0.18	1.5	206	135	78	11	0.01	2	2.9	4.6	28	0.1
KL40-08	302.7	305.7	0.0035	35	0.15	4.7	650	500	56	6	0.01	3	4.2	10.3	18	0.01
KL40-08	305.7	308.7	0.0076	76	0.08	1.1	920	600	53	13	1	3	3.3	6.3	30	0.01
KL40-08	308.7	311.7	0.04	400	1.71	13.4	10800	4900	250	25	4	3	22.3	68.0	38	0.39
KL40-08	311.7	314.7	0.0095	95	0.25	3.6	2300	1300	97	37	11	1	5.3	8.5	28	0.11
KL40-08	314.7	317.7	0.0096	96	0.26	3.6	2300	1320	58	40	6	1	5.6	12.3	30	0.1
KL40-08	317.7	320.7	0.0052	52	0.06	0.9	1020	359	23	10	1	1	2.4	2.0	24	0.01
KL40-08	320.7	323.7	0.0369	369	1.72	11.6	11100	5000	250	25	3	4	22	75.0	41	0.39
KL40-08	323.7	326.7	0.011	110	0.05	2.4	2150	1480	55	8	2	1	2.3	15.8	24	0.01
KL40-08	326.7	329.7	0.56	5600	0.15	8.7	2500	312	35	86	2	18	2.6	11.5	24	0.01
KL40-08	329.7	332.7	0.063	630	0.04	1.4	1330	530	30	54	2	3	2.8	3.8	29	0.01
KL40-08	332.7	335.7	0.064	640	0.03	1.9	1420	630	36	56	2	4	2.7	4.5	28	0.01
KL40-08	335.7	338.7	0.27	2700	0.29	6.3	13600	1420	190	93	48	12	5	33.5	29	0.12
KL40-08	338.7	341.7	0.107	1070	0.17	2.7	5300	560	77	34	13	5	2.8	15.0	34	0.1
KL40-08	341.7	344.7	0.172	1720	0.37	2.7	1570	620	180	191	20	7	6.7	3.5	38	0.01
KL40-08	344.7	347.7	0.0138	138	0.5	3	3800	1360	250	55	3	3	8.4	2.8	32	0.7
KL40-08	347.7	350.7	0.177	1770	1.02	13.2	32300	7500	490	83	5	5	37	5.0	51	0.76
KL40-08	350.7	353.7	0.0037	37	0.06	1.1	470	116	32	55	1	2	1.3	0.0	29	0.01
KL40-08	353.7	356.7	0.028	280	0.28	8.6	9200	4500	260	136	1	1	11.3	1.5	29	0.13
KL40-08	356.7	359.7	0.0204	204	0.72	7.2	6400	3700	260	38	2	3	15.3	1.3	27	0.14
KL40-08	359.7	362.7	0.0103	103	0.05	0.5	386	134	88	7	0.01	2	1.1	0.6	34	0.01
KL40-08	362.7	365.7	0.0035	35	0.05	0.5	399	127	35	64	1	2	1.1	0.0	28	0.01
KL40-08	365.7	368.7	0.0069	69	0.01	0.1	325	130	13	4	0.01	1	0.5	1.0	30	0.01
KL40-08	368.7	371.7	0.0081	81	0.08	1.3	1320	810	57	10	2	3	2.8	11.0	26	0.01
KL40-08	371.7	374.7	0.0039	39	0.06	0.9	850	340	28	9	1	3	2.4	3.0	25	0.01
KL40-08	374.7	377.1	0.004	40	0.03	0.1	210	103	16	4	0.01	1	0.6	0.0	16	0.01
KL40-08	377.1	380.2	0.0041	41	0.02	0.1	560	410	20	31	2	1	1	0.0	23	0.01
KL40-08	380.2	383.3	0.0114	114	0.5	3.5	3200	1360	260	55	5	3	8.5	2.0	29	0.52
KL40-08	383.3	386.4	0.047	470	0.31	0.7	120	110	260	146	41	5	2.5	3.0	47	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL40-08	386.4	389.5	0.171		1710	0.39	2.9	1750	900	230	193	17	6	4.8	6.3	34	0.01
KL40-08	389.5	392.6	0.0229		229	0.1	0.1	610	39	42	73	7	2	1	1.0	33	0.01
KL40-08	392.6	395.6	0.164		1640	0.38	2.3	800	248	130	82	4	5	3.9	4.5	34	0.01
KL40-08	395.6	398.6	0.093		930	0.11	0.6	335	62	29	71	1	3	1.3	2.3	24	0.01
KL40-08	398.6	401.6	0.0071		71	0.35	0.1	920	580	150	62	0.01	4	4	3.3	41	0.27
KL40-08	401.6	404.6	0.0113		113	0.51	0.1	244	87	250	25	1	2	3.8	6.3	36	0.52
KL40-08	404.6	407.6	0.0128		128	0.2	0.1	402	36	45	14	0.01	2	1.3	1.3	21	0.01
KL40-08	407.6	410.6	0.95		9500	3.61	4.9	22500	150	320	1290	38	29	12.8	31.3	56	0.01
KL40-08	410.6	413.1	0.066		660	0.88	0.1	278	32	150	620	14	5	3.3	2.0	44	0.01
KL40-08	413.1	416.2	0.056		560	1.7	1.6	800	600	440	2250	14	4	13.3	8.5	42	0.01
KL40-08	416.2	419.3	0.0241		241	0.28	0.1	480	94	200	405	4	3	2.9	2.0	45	0.01
KL40-08	419.3	422.5	0.57		5700	1.97	3.2	3900	165	290	430	28	19	14.3	8.0	49	0.1
KL40-08	422.5	425.6	0.189		1890	1.18	1.8	2900	204	250	890	40	6	1.2	8.5	82	0.01
KL40-08	425.6	428.6	0.527		5270	1.62	3.4	6800	270	210	570	40	28	10	13.5	71	0.12
KL40-08	428.6	431	0.0276		276	0.34	0.7	590	385	190	1050	12	3	3.7	4.3	55	0.01
KL40-08	431	434.1	0.0361		361	0.41	0.5	285	107	110	760	5	2	3.8	1.8	62	0.01
KL40-08	434.1	437.1	0.78		7800	0.7	11.5	3400	3000	480	759	13	3	26	4.5	82	0.29
KL40-08	437.1	440.1	0.29		2900	2.39	22.9	17500	6900	1160	1290	46	2	60	21.0	99	0.1
KL40-08	440.1	443.2	0.151		1510	0.27	1.1	940	62	180	367	9	4	6	3.6	43	0.01
KL40-08	443.2	446.3	2.72		27200	2.88	17.6	700	120	440	62	24	49	14	5.0	62	0.01
KL40-08	446.3	449.4	0.055		550	1.11	1.5	580	167	760	1090	38	2	16	4.5	55	0.01
KL40-08	449.4	452.5	0.31		3100	0.53	1.7	176	72	460	810	12	3	18	7.0	34	0.01
KL40-08	452.5	455.6	0.0163		163	0.18	0.8	280	103	52	380	1	1	6.5	1.8	95	0.01
KL40-08	455.6	458.6	0.0192		192	0.13	0.5	80	34	110	174	1	2	4	1.3	65	0.01
KL40-08	458.6	461.6	0.0174		174	0.11	0.1	77	30	47	530	8	3	3.1	5.0	64	0.01
KL40-08	461.6	464.6	0.0216		216	0.08	0.1	210	54	43	276	0.01	1	1.9	0.8	117	0.01
KL40-08	464.6	467.6	0.0141		141	0.06	0.1	108	26	51	445	1	1	2.4	0.7	78	0.01
KL40-08	467.6	470.6	0.0215		215	0.09	0.1	210	58	39	263	0.01	1	2.3	1.3	110	0.01
KL40-08	470.6	472	0.26		2600	2.44	7.1	570	430	710	90	49	2	7.6	12.5	52	0.01
KL40-08	472	473.7	0.0371		371	0.16	0.1	186	76	51	19	1	2	0.9	3.5	21	0.01
KL40-08	473.7	476.6	0.0184		184	0.19	0.1	97	86	50	18	1	1	2.2	1.5	19	0.01
KL40-08	476.6	479.6	0.043		430	0.27	0.1	4400	480	230	9	1	1	2.3	2.3	20	0.01
KL40-08	479.6	482.6	0.0094		94	0.03	0.1	231	73	27	11	0.01	1	0.8	1.8	19	0.01
KL40-08	482.6	485.6	0.106		1060	0.11	0.5	430	86	45	6	1	1	1.3	3.5	21	0.01
KL40-08	485.6	486.7	0.0109		109	0.04	0.1	298	43	28	5	0.01	1	0.8	2.0	19	0.01
KL40-08	486.7	489.7	0.0131		131	0.02	0.1	49	20	21	5	0.01	1	1.3	1.5	17	0.01
KL40-08	489.7	492.2	0.0069		69	0.03	0.1	250	67	26	8	0.01	1	1	0.7	20	0.01
KL40-08	492.2	495	0.088		880	0.14	0.1	1050	144	70	5	0.01	1	2.5	2.2	17	0.01
KL40-09	0	4.2	0.0208		208	0.03	8.7	5300	9100	25	15	0.01	5	16	118.0	20	0.01
KL40-09	4.2	6.9	0.0229		229	0.11	1.4	1210	480	29	224	3	2	8.3	4.6	29	0.01
KL40-09	6.9	9.4	0.221		2210	0.06	1.9	560	1120	14	9	3	2	4.9	7.5	12	0.01
KL40-09	9.4	11.3	0.0077		77	0.08	0.6	318	130	27	10	0.01	1	6.3	0.8	17	0.01
KL40-09	11.3	13.2	0.0075		75	0.08	0.6	351	133	23	28	2	1	6.1	1.8	72	0.01
KL40-09	13.2	15.4	0.535		5350	0.14	2.4	620	860	16	15	5	5	5.8	5.3	20	0.12
KL40-09	15.4	18	0.0051		51	0.05	0.9	540	278	15	13	0.01	1	3.2	2.0	18	0.01
KL40-09	18	20.7	0.0041		41	0.03	1.3	560	331	20	3	2	1	6.7	2.4	18	0.1
KL40-09	20.7	22.7	0.068		680	0.12	1.1	650	265	27	40	2	3	3.9	3.3	57	0.1
KL40-09	22.7	25.7	0.0114		114	0.05	2.8	1010	1060	22	16	7	1	12.1	5.8	21	0.26
KL40-09	25.7	28.6	0.9		9000	0.19	5.6	1180	3200	15	9	8	8	9.5	9.0	28	0.31
KL40-09	28.6	31.8	0.0089		89	0.09	2.3	710	830	37	17	4	1	5.9	11.5	23	0.01
KL40-09	31.8	34.9	0.0043		43	0.04	1.2	430	162	17	11	6	1	5.8	2.3	20	0.1
KL40-09	34.9	37.9	0.0042		42	0.04	0.6	910	163	32	60	5	1	15.6	2.0	22	0.16
KL40-09	37.9	41	0.0068		68	0.03	0.9	710	180	25	38	6	1	6.2	3.2	19	0.01
KL40-09	41	44.1	0.0055		55	0.14	1.9	890	280	64	227	22	1	10.8	3.8	36	0.01
KL40-09	44.1	47.1	0.046		460	0.09	2.3	1390	530	76	21	16	3	24	7.8	40	0.21
KL40-09	47.1	48.8	0.0343		343	0.13	1.6	1570	570	120	230	11	2	26	4.3	30	0.12
KL40-09	48.8	50.7	0.0161		161	0.04	1.3	281	128	30	345	19	1	3.6	3.3	32	0.01
KL40-09	50.7	53.7	0.0343		343	0.08	2.1	5030	620	44	52	16	2	7	9.4	21	0.01
KL40-09	53.7	56.7	0.095		950	0.07	0.9	530	285	30	19	4	1	2	7.8	39	0.01
KL40-09	56.7	59.7	0.0185		185	0.06	1.4	740	196	45	53	24	1	5	5.5	23	0.01
KL40-09	59.7	62.3	0.097		970	0.07	0.6	250	89	34	63	16	2	1.7	5.5	67	0.01
KL40-09	62.3	64.3	0.108		1080	0.05	1.1	780	386	15	41	4	4	2.3	6.3	17	0.01
KL40-09	64.3	67.5	0.0043		43	0.01	0.6	640	129	35	11	3	1	3.7	1.8	33	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL40-09	67.5	70.7	0.0098		98	0.03	0.6	470	230	39	9	3	1	8	1.3	26	0.01
KL40-09	70.7	73.7	0.0054		54	0.02	0.7	470	210	32	17	3	1	4.3	1.5	23	0.01
KL40-09	73.7	76.9	0.0084		84	0.01	0.7	214	184	34	7	4	2	1.3	1.3	20	0.01
KL40-09	76.9	78.7	0.044		440	0.02	1	730	243	71	40	24	2	3.1	4.3	24	0.01
KL40-09	78.7	81.1	0.072		720	0.32	2.1	640	346	140	335	12	12	5.8	8.6	72	0.01
KL40-09	81.1	84.1	0.046		460	0.12	2.3	1350	1950	130	215	9	12	11.2	8.3	31	0.01
KL40-09	84.1	86.7	0.0417		417	0.48	2.1	2180	610	190	15	12	4	34	7.5	76	0.43
KL40-09	86.7	89.7	0.0211		211	0.09	2	720	460	92	10	14	5	12	5.0	32	0.01
KL40-09	89.7	92.1	0.033		330	0.08	3.4	2370	650	80	20	19	5	40	6.8	29	0.26
KL40-09	92.1	94.9	0.0181		181	0.12	1.6	1400	440	100	26	6	4	24	7.5	32	0.01
KL40-09	94.9	97.2	0.0061		61	0.07	1.4	600	262	60	15	8	2	5.7	2.0	26	0.01
KL40-09	97.2	98.7	0.0051		51	0.1	1.4	980	630	35	18	4	2	7.3	2.5	25	0.01
KL40-09	98.7	101.1	0.0012		12	0.03	0.7	660	178	7	1	0.01	1	3.1	1.5	19	0.01
KL40-09	101.1	104.2	0.0082		82	0.04	1.2	4200	1000	12	16	2	2	4.7	7.0	23	0.01
KL40-09	104.2	105.4	0.113		1130	0.15	28.9	46200	15500	140	18	34	2	18	485.0	47	0.15
KL40-09	105.4	107.7	0.0047		47	0.03	1.4	1140	520	19	3	0.01	1	2.5	13.8	27	0.01
KL40-09	107.7	110.7	0.0046		46	0.03	2.1	8900	1040	20	3	1	2	5.5	4.5	33	0.01
KL40-09	110.7	113.7	0.0358		358	0.21	9.9	30500	8400	50	7	0.01	6	20	11.5	43	0.14
KL40-09	113.7	116.7	0.0209		209	3.21	13.6	14200	7800	100	20	1	2	14	16.5	55	0.19
KL40-09	116.7	119.7	0.05		500	0.53	7.6	3500	6700	260	23	3	2	18.4	45.0	45	0.24
KL40-09	119.7	122.7	0.0052		52	0.07	1.6	580	310	30	24	5	2	3.3	5.8	22	0.01
KL40-09	122.7	125.7	0.0142		142	0.3	7.7	1420	530	76	15	14	1	17.9	9.0	24	0.19
KL40-09	125.7	128.7	0.0047		47	0.09	0.6	384	283	25	5	1	1	2	7.8	19	0.01
KL40-09	128.7	131.7	0.0062		62	0.04	0.6	425	203	26	18	2	1	2.5	4.0	35	0.01
KL40-09	131.7	134.2	0.08		800	0.07	0.8	570	375	28	12	2	1	2	6.8	36	0.01
KL40-09	134.2	137.2	0.0223		223	0.08	2.6	820	710	100	18	14	2	9.5	6.5	37	0.16
KL40-09	137.2	139.4	0.0376		376	0.16	2.9	3180	1000	57	18	4	3	8.7	23.2	104	0.17
KL40-09	139.4	142.4	0.0039		39	0.06	1	900	300	35	13	2	1	3.5	2.5	94	0.1
KL40-09	142.4	144.6	0.0042		42	0.06	0.9	860	283	26	18	1	1	3	2.9	97	0.1
KL40-09	144.6	146.3	0.0129		129	0.03	0.5	560	189	21	45	1	1	2.3	2.0	61	0.01
KL40-09	146.3	148.8	0.56		5600	1.02	11.7	1310	1270	1490	581	18	11	60	27.5	76	0.17
KL40-09	148.8	151.5	0.76		7600	0.44	6.8	181	136	2580	395	3	13	105	7.9	358	0.18
KL40-09	151.5	154.7	0.73		7300	0.34	6.1	134	123	2410	110	2	4	84	5.0	266	0.12
KL40-09	154.7	157.8	0.52		5200	0.36	7.1	260	312	1700	139	5	5	52	5.0	284	0.25
KL40-09	157.8	159.3	0.64		6400	0.31	5.3	101	77	2040	660	3	4	68	5.3	229	0.18
KL40-09	159.3	161.7	0.94		9400	0.44	5.6	80	104	2960	60	1	3	115	4.0	265	0.12
KL40-09	161.7	164.7	0.54		5400	0.24	3.9	75	91	2040	103	2	2	46	2.3	172	0.14
KL40-09	164.7	167.7	0.85		8500	0.17	8.8	147	140	2320	314	7	4	70	7.0	321	0.35
KL40-09	167.7	170.7	1.4		14000	1.06	8.9	258	129	2670	350	3	2	118	4.5	130	0.43
KL40-09	170.7	173.7	0.55		5500	1.08	10.3	184	108	1750	1910	5	4	72	8.4	291	0.34
KL40-09	173.7	176.7	0.275		2750	0.81	7	75	93	780	1100	6	5	42	6.8	127	0.18
KL40-09	176.7	179.7	0.192		1920	0.75	6.5	560	198	490	1180	6	6	30	9.8	213	0.29
KL40-09	179.7	182.7	0.136		1360	1.59	5.4	470	244	260	5300	8	4	50	14.0	221	0.33
KL40-09	182.7	185.7	0.338		3380	6.36	15.3	341	750	480	2630	44	10	63	17.2	97	0.57
KL40-09	185.7	188.8	0.26		2600	2.31	12.3	4480	1220	210	1160	23	18	24	11.3	72	0.32
KL40-09	188.8	191.7	0.12		1200	0.49	3.5	5270	1210	89	1170	13	13	17.4	12.5	48	0.21
KL40-09	191.7	194.7	0.096		960	0.37	2.2	4300	900	71	411	20	10	8.4	7.0	25	0.15
KL40-09	194.7	196.6	0.0386		386	2.81	1.5	2100	610	26	207	9	3	2.6	6.5	28	0.01
KL40-09	196.6	198.4	0.22		2200	0.34	4.2	8740	1670	100	354	14	8	8.8	12.0	32	0.16
KL40-09	198.4	200.1	0.083		830	0.45	2.1	3150	920	59	327	18	6	6.8	10.0	28	0.01
KL40-09	200.1	202.7	0.075		750	0.14	2	3100	910	77	329	12	3	4.2	8.8	32	0.16
KL40-09	202.7	204.6	0.058		580	0.15	2.1	1970	500	43	142	16	1	2.1	13.0	46	0.01
KL40-09	204.6	206.7	0.074		740	0.09	1.3	1170	176	20	53	8	1	1.3	9.3	36	0.01
KL40-09	206.7	209.7	0.0112		112	0.08	0.6	348	146	16	87	4	1	1	1.5	21	0.01
KL40-09	209.7	211.7	0.0067		67	0.03	0.1	156	55	7	70	3	1	0.5	3.0	28	0.01
KL40-09	211.7	214.5	0.063		630	0.14	2	970	263	29	248	12	3	3.9	10.0	31	0.01
KL40-09	214.5	215.3	0.121		1210	0.24	3.6	1530	303	56	331	24	10	9.1	15.0	32	0.01
KL40-09	215.3	217.8	0.0176		176	0.04	1.7	740	287	18	116	15	1	1.8	6.2	18	0.01
KL40-09	217.8	220.4	0.052		520	0.16	1.6	2240	600	54	270	12	4	4.7	7.3	31	0.01
KL40-09	220.4	222.1	0.095		950	0.21	3	1630	830	200	248	14	4	19.6	12.5	32	0.01
KL40-09	222.1	224.3	0.077		770	0.1	1.9	1310	550	100	64	9	4	15.2	9.0	28	0.01
KL40-09	224.3	227.5	0.0244		244	0.09	0.8	320	400	52	99	3	2	6.1	4.5	29	0.01
KL40-09	227.5	230	0.0296		296	0.16	0.9	2070	266	61	26	6	3	7.9	5.5	28	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL40-09	230	232.4	0.0145	145	0.03	1.5	670	211	12	112	10	1	1	6.0	20	0.01
KL40-09	232.4	234.7	0.0055	55	0.03	0.9	1000	364	9	15	2	1	1.3	2.5	11	0.01
KL40-09	234.7	236.5	0.017	170	0.03	0.6	470	191	51	44	28	1	3.1	9.5	11	0.01
KL40-09	236.5	238	0.0126	126	0.04	0.8	510	271	13	42	7	1	1.2	3.5	12	0.01
KL40-09	238	239.9	0.0365	365	0.11	1.8	2400	630	130	185	20	3	20	8.5	24	0.12
KL40-09	239.9	242.1	0.069	690	0.13	1.8	1200	351	210	236	36	6	24	10.3	16	0.1
KL40-09	242.1	244	0.0106	106	0.04	0.6	440	147	17	38	5	1	1.3	3.9	11	0.01
KL40-09	244	246.2	0.0195	195	0.04	1.8	800	320	25	65	8	1	2.8	6.0	13	0.01
KL40-09	246.2	247.9	0.0203	203	0.02	0.1	530	160	25	10	2	1	2.4	3.0	10	0.01
KL40-09	247.9	249.7	0.003	30	0.02	0.1	800	197	4	7	1	1	0.4	1.8	15	0.01
KL40-09	249.7	251.8	0.0225	225	0.02	0.1	820	380	23	8	1	1	1.9	2.3	12	0.01
KL40-09	251.8	254.8	0.091	910	0.05	0.9	880	281	14	55	6	4	2	7.8	12	0.01
KL40-09	254.8	256.3	0.07	700	0.11	1.3	710	275	45	67	2	4	4.1	8.1	47	0.01
KL40-09	256.3	257.8	0.0144	144	0.03	0.1	650	67	10	208	2	1	0.8	3.3	11	0.01
KL40-09	257.8	260.9	0.056	560	0.08	9.2	16000	4210	34	500	46	7	14	20.0	14	0.14
KL40-09	260.9	263.1	0.053	530	0.1	5	10700	1100	68	58	42	3	10.5	18.5	18	0.01
KL40-09	263.1	265.8	0.0251	251	0.03	3.1	4000	1430	22	112	8	1	2.1	8.0	14	0.01
KL40-09	265.8	267.5	0.0119	119	0.02	0.1	800	160	15	120	2	1	1	3.0	12	0.01
KL40-09	267.5	269.7	0.043	430	0.04	1.4	850	373	31	39	2	1	7.6	6.3	14	0.01
KL40-09	269.7	271.9	0.0154	154	0.05	1	2010	320	21	55	3	1	3.2	5.8	12	0.01
KL40-09	271.9	275	0.0347	347	0.04	3.1	1560	328	30	130	34	1	1.3	26.3	19	0.01
KL40-09	275	277.1	0.081	810	0.16	15.5	3400	1220	240	286	180	5	4.6	80.0	16	0.01
KL40-09	277.1	279.9	0.048	480	0.24	1.3	1730	180	130	278	10	3	6.1	10.2	14	0.01
KL40-09	279.9	282.9	0.094	940	0.07	0.9	2230	89	120	580	4	4	5.5	12.5	18	0.01
KL40-09	282.9	286	0.0267	267	0.06	0.7	950	240	37	188	3	1	4	8.0	19	0.01
KL40-09	286	288.9	0.043	430	0.07	1.1	1070	180	57	133	5	3	6.2	7.4	14	0.01
KL40-09	288.9	291.7	0.0392	392	0.06	0.1	820	136	25	58	5	1	3	9.3	13	0.01
KL40-09	291.7	293.3	0.0174	174	0.04	0.6	216	87	18	131	3	1	3	3.9	14	0.01
KL40-09	293.3	296.2	0.041	410	0.05	1	560	166	13	79	6	1	2.3	7.8	14	0.01
KL40-09	296.2	298.8	0.0085	85	0.01	0.1	288	44	5	33	3	1	0.5	1.5	11	0.01
KL40-09	298.8	301.3	0.0245	245	0.02	0.7	329	277	8	78	4	1	0.6	5.0	13	0.01
KL40-09	301.3	302.8	0.295	2950	0.12	1.1	460	308	15	23	4	2	0.8	8.8	18	0.01
KL40-09	302.8	305.9	0.062	620	0.05	0.9	2450	1410	25	18	3	1	2.1	20.8	12	0.01
KL40-09	305.9	308.9	0.113	1130	0.05	1.4	1180	650	19	20	4	2	1.4	13.8	16	0.01
KL40-09	308.9	311.9	0.151	1510	0.18	1.1	356	167	19	15	5	1	0.9	7.8	12	0.01
KL40-09	311.9	314.9	0.73	7300	0.55	2.8	790	144	41	65	14	10	1.7	26.0	28	0.01
KL40-09	314.9	317.3	2.34	23400	1.39	5.5	159	17	35	90	5	21	1.1	33.0	24	0.01
KL40-09	317.3	320.4	1.36	13600	0.73	1.7	198	34	9	24	56	18	4.9	11.5	20	0.01
KL40-09	320.4	323.3	1.73	17300	0.37	3	268	13	12	30	12	18	4.2	13.5	34	0.01
KL40-09	323.3	326.4	3.78	37800	0.44	5.2	266	12	4	171	7	19	5.6	22.5	38	0.01
KL40-09	326.4	329.5	2.23	22300	0.32	4.7	284	21	10	37	8	21	5.9	11.0	25	0.01
KL40-09	329.5	332.6	1.52	15200	0.29	3.1	253	44	7	172	18	15	9.5	8.5	30	0.01
KL40-09	332.6	335.7	2.04	20400	0.28	5	163	14	5	10	20	15	4.1	9.8	24	0.01
KL40-09	335.7	337.4	3.32	33200	0.6	5.4	197	14	3	4	42	19	2.3	17.5	25	0.01
KL40-09	337.4	338.9	4.67	46700	0.71	3.7	216	19	6	363	4	20	3.7	21.3	35	0.01
KL40-09	338.9	341.3	4.82	48200	1.3	4.4	319	5	3	210	2	27	0.5	27.5	22	0.01
KL40-09	341.3	344.4	0.164	1640	0.07	0.6	78	89	19	19	1	9	1.8	8.3	33	0.01
KL40-09	344.4	346	0.171	1710	0.06	1.4	670	560	17	99	2	5	1.7	11.7	32	0.01
KL40-09	346	349.1	0.59	5900	0.3	1.6	62	16	14	54	1	21	0.2	11.8	21	0.01
KL40-09	349.1	351.8	0.167	1670	0.06	0.8	71	41	7	265	0.01	4	0.4	6.0	29	0.01
KL40-09	351.8	354.9	0.37	3700	0.4	6.8	1180	1500	170	660	9	7	32	13.2	36	0.1
KL40-09	354.9	356.7	0.078	780	0.07	0.7	243	460	26	23	0.01	5	4.5	8.3	17	0.01
KL40-09	356.7	359.5	0.354	3540	0.08	0.9	113	31	39	16	5	5	2.8	2.3	31	0.01
KL40-09	359.5	361.9	0.56	5600	0.2	1.1	248	25	25	166	1	29	0.4	7.0	31	0.01
KL40-09	361.9	364.1	0.375	3750	0.28	1.2	148	10	16	36	1	19	1	2.0	19	0.01
KL40-09	364.1	366.4	0.336	3360	0.08	0.9	87	54	12	22	0.01	4	2.6	2.1	10	0.01
KL40-09	366.4	368.7	0.22	2200	0.16	0.8	70	18	11	14	0.01	8	0.9	1.5	13	0.01
KL40-09	368.7	371	0.134	1340	0.13	0.1	320	45	28	10	0.01	25	0.8	3.5	16	0.01
KL40-09	371	373.7	0.14	1400	0.08	0.1	17300	14	8	4	0.01	80	12.3	5.5	27	0.01
KL40-09	373.7	375.8	0.84	8400	0.48	2.9	4800	32	9	12	0.01	50	0.9	9.7	16	0.01
KL40-09	375.8	377.9	0.88	8800	0.38	2.2	840	16	20	11	0.01	30	0.7	7.0	18	0.01
KL40-09	377.9	380.7	0.37	3700	0.29	1.3	3000	28	23	10	1	25	1.8	6.0	32	0.01
KL40-09	380.7	383.7	0.399	3990	0.55	1.5	144	22	38	14	7	8	5.2	4.0	24	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL40-09	383.7	386.7	0.362	3620	0.2	0.7	113	26	26	31	2	7	5	3.8	30	0.01
KL40-09	386.7	389.7	0.22	2200	0.14	1	95	24	22	162	1	8	4.6	4.6	42	0.01
KL40-09	389.7	392.2	1.25	12500	0.67	5.7	338	21	29	21	35	33	4.2	9.5	25	0.01
KL40-09	392.2	394.1	0.296	2960	0.18	1.4	381	15	26	9	3	9	1.8	11.0	21	0.01
KL40-09	394.1	395.8	0.62	6200	0.31	1.2	440	15	28	18	1	10	0.8	3.8	20	0.01
KL40-09	395.8	398.2	0.196	1960	0.1	0.8	510	13	30	9	1	11	2	2.8	56	0.01
KL40-09	398.2	401.2	0.65	6500	0.26	2.5	740	21	13	9	11	22	10.8	4.8	29	0.01
KL40-09	401.2	404.3	0.067	670	0.07	0.1	191	13	15	5	1	5	0.8	1.0	30	0.01
KL40-09	404.3	406.4	0.075	750	0.04	0.1	285	11	22	8	0.01	2	2.1	1.3	17	0.01
KL40-09	406.4	407.9	0.095	950	0.06	0.1	570	44	34	7	0.01	3	1.1	2.3	19	0.01
KL40-09	407.9	410.9	0.456	4560	0.27	2.1	520	51	15	10	4	15	8.5	5.3	24	0.01
KL40-09	410.9	413.9	1.2	12000	0.48	3.8	332	10	4	9	14	25	5.8	12.5	23	0.01
KL40-09	413.9	416.9	0.409	4090	0.25	1.6	440	12	19	10	7	16	4.7	9.0	42	0.01
KL40-09	416.9	419.9	1.02	10200	0.47	2.2	279	44	28	8	5	19	5.8	13.0	40	0.01
KL40-09	419.9	422.9	4.38	43800	1.35	6.6	2500	21	13	9	2	47	1.5	32.5	25	0.01
KL40-09	422.9	425.7	1.98	19800	0.95	2.3	900	10	1	4	3	45	0.9	16.0	24	0.01
KL40-09	425.7	428.7	2.41	24100	0.98	4.6	16000	10	2	7	7	96	1	21.5	32	0.01
KL40-09	428.7	431.7	2.03	20300	0.71	3.8	1760	10	2	5	10	87	0.8	24.0	17	0.01
KL40-09	431.7	434	2.02	20200	1.07	5.4	7000	11	4	5	60	119	1	17.5	20	0.01
KL40-09	434	438.7	1.88	18800	0.64	2.9	2090	12	6	4	7	85	2.2	14.0	38	0.01
KL40-09	438.7	440.7	1.64	16400	0.3	2	16200	14	2	2	4	115	7.3	11.0	78	0.01
KL40-09	440.7	443.7	1.7	17000	0.62	3.3	5000	16	0.01	7	8	84	2.8	14.0	33	0.01
KL40-09	443.7	446.7	2.8	28000	1.52	4.2	1750	9	1	3	6	74	1.2	12.0	59	0.01
KL40-09	446.7	449.7	1.46	14600	1.11	10.5	1950	640	9	5	40	120	7.5	16.0	30	0.01
KL40-09	449.7	450.5	1.1	11000	0.76	1.6	2700	17	4	3	2	104	2.8	13.7	45	0.01
KL40-09	450.5	452.7	0.424	4240	0.48	1.1	188	42	10	329	2	14	1.2	5.3	93	0.01
KL40-09	452.7	454.3	0.185	1850	0.09	1.3	321	168	2	24	3	12	0.01	4.0	70	0.01
KL40-09	454.3	456.2	0.55	5500	0.17	0.8	158	37	6	20	1	10	0.5	6.4	77	0.01
KL40-09	456.2	458.2	0.22	2200	0.16	0.9	202	96	3	21	1	6	0.4	4.8	106	0.01
KL40-09	458.2	461.2	0.349	3490	0.21	1.1	186	68	3	81	1	8	0.7	3.9	98	0.01
KL40-09	461.2	463.3	0.116	1160	0.09	0.6	121	67	13	108	1	5	3.3	5.3	112	0.01
KL40-09	463.3	466.1	0.164	1640	0.14	0.6	65	20	7	19	0.01	5	0.5	1.8	82	0.01
KL40-09	466.1	469.2	0.21	2100	0.15	0.7	61	18	9	11	0.01	7	2.4	2.0	30	0.01
KL40-09	469.2	471.6	0.22	2200	0.32	0.8	48	15	3	8	1	5	0.01	3.0	28	0.01
KL40-09	471.6	473.8	0.24	2400	0.39	0.9	73	12	4	156	0.01	4	0.01	2.5	91	0.01
KL40-09	473.8	476.8	0.22	2200	0.38	0.6	45	17	4	9	0.01	6	0.5	2.3	64	0.01
KL40-09	476.8	479.8	0.175	1750	0.17	0.1	68	38	4	10	0.01	5	0.9	2.3	49	0.01
KL40-09	479.8	482.8	0.34	3400	0.15	0.8	74	24	14	11	2	3	1.6	4.5	97	0.01
KL40-09	482.8	485.8	0.169	1690	0.15	0.8	75	50	4	12	0.01	3	1	3.0	71	0.01
KL40-09	485.8	488.8	0.499	4990	0.22	0.9	65	17	2	18	0.01	6	0.01	3.3	60	0.01
KL40-09	488.8	491.9	0.54	5400	0.12	2	660	410	20	108	2	7	1.7	8.8	111	0.01
KL40-09	491.9	494.9	0.29	2900	0.14	1.2	61	20	2	19	1	10	0.3	3.8	64	0.01
KL40-09	494.9	497.7	0.403	4030	0.5	1.1	88	18	4	7	1	6	0.2	3.5	41	0.01
KL40-09	497.7	500.7	0.29	2900	0.24	1.2	40	22	1	6	1	4	0.3	2.8	55	0.01
KL40-09	500.7	503.7	0.461	4610	0.35	1.6	95	45	4	4	1	5	0.3	5.3	54	0.01
KL40-09	503.7	506.7	1.68	16800	0.93	5.7	251	168	36	30	11	4	10.5	3.9	126	0.19
KL40-09	506.7	509.7	0.432	4320	0.32	4.4	83	61	16	301	40	4	2.4	5.0	61	0.01
KL40-09	509.7	511.2	0.178	1780	0.17	1.1	72	30	2	11	1	6	0.3	2.6	58	0.01
KL40-09	511.2	512.7	0.162	1620	0.39	2.3	88	37	13	7	7	6	2	3.3	72	0.01
KL40-09	512.7	515.7	0.188	1880	0.22	1.1	146	68	3	15	1	4	0.3	2.0	72	0.01
KL40-09	515.7	518.7	0.22	2200	0.23	1.9	510	1350	9	9	1	6	0.6	1.3	65	0.01
KL40-09	518.7	521.7	0.23	2300	0.49	1.3	97	53	7	5	3	7	0.9	2.3	82	0.01
KL40-09	521.7	524.7	0.145	1450	0.35	1.8	121	64	18	4	4	6	1.3	2.5	63	0.01
KL40-09	524.7	527.6	0.213	2130	0.29	1.3	126	53	10	2	4	8	0.4	3.7	59	0.01
KL40-09	527.6	529.5	0.24	2400	0.19	1	57	23	3	7	0.01	6	0.4	3.6	95	0.01
KL40-09	529.5	530.9	0.098	980	0.04	0.9	70	34	6	35	1	3	0.7	1.6	169	0.01
KL40-09	530.9	533.9	0.065	650	0.06	1	84	51	12	58	2	6	1.6	7.0	257	0.01
KL40-09	533.9	536.9	0.141	1410	0.04	1.4	161	214	8	425	3	1	3.3	1.9	173	0.01
KL40-09	536.9	538.9	0.62	6200	0.74	3.1	1260	1170	1860	25	3	2	110	5.8	153	0.17
KL40-09	538.9	540.5	0.148	1480	0.33	1.7	180	131	180	86	3	2	30	6.0	179	0.01
KL40-09	540.5	542.7	0.417	4170	1.19	4.1	78	98	380	42	5	2	18.4	5.5	160	0.1
KL40-09	542.7	545.7	0.23	2300	0.09	1	27	23	27	86	1	3	6.3	1.7	187	0.01
KL40-09	545.7	548.7	0.189	1890	0.04	0.8	31	30	12	45	1	3	1.8	3.5	211	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL40-09	548.7	550.1	0.21	2100	0.07	0.8	37	60	3	35	1	4	1.9	3.1	188	0.01
KL40-09	550.1	553.3	0.159	1590	0.05	0.7	100	37	6	23	2	3	2	4.0	233	0.01
KL40-09	553.3	556.5	0.168	1680	0.11	1.1	43	23	4	18	2	5	1.6	8.3	204	0.01
KL40-09	556.5	559.6	0.115	1150	0.06	0.6	25	16	40	21	1	2	7.5	3.5	193	0.01
KL40-09	559.6	561.4	0.078	780	0.24	1	510	59	120	62	4	4	17.7	8.8	181	0.01
KL40-09	561.4	563.7	0.078	780	0.15	0.7	96	48	130	17	3	3	42	5.8	193	0.01
KL40-09	563.7	566.7	0.089	890	0.05	0.6	70	36	170	26	2	2	20	2.5	154	0.01
KL40-09	566.7	569.7	0.165	1650	0.08	0.9	118	41	210	33	2	2	26	4.0	156	0.01
KL40-09	569.7	572.7	0.476	4760	0.14	0.7	104	32	460	71	2	2	26	3.5	188	0.01
KL40-09	572.7	575.7	0.24	2400	0.15	1.1	155	42	570	40	2	2	42	3.5	183	0.01
KL40-09	575.7	578.2	0.193	1930	0.44	1.3	135	57	60	193	5	9	24	11.5	168	0.01
KL40-09	578.2	581.4	0.075	750	0.08	0.6	92	27	160	73	2	5	28	4.3	179	0.01
KL40-09	581.4	584.6	0.22	2200	0.17	1.4	181	43	480	153	3	4	40	8.5	178	0.01
KL40-09	584.6	587.7	0.36	3600	0.22	2.1	309	80	160	15	3	4	8.4	2.3	239	0.01
KL40-09	587.7	590.2	0.221	2210	0.25	1.9	450	68	160	824	9	5	17.3	9.3	236	0.01
KL40-09	590.2	593.3	0.195	1950	0.2	1.6	416	39	510	217	2	3	66	4.2	117	0.01
KL40-09	593.3	595	0.165	1650	0.22	1	580	193	400	235	6	3	70	8.5	171	0.01
KL40-09	595	596.7	0.489	4890	0.26	1.9	500	1430	660	136	2	3	48	2.3	48	0.11
KL40-09	596.7	599.7	0.67	6700	0.47	1.7	31	17	110	25	1	2	20	0.8	147	0.01
KL40-09	599.7	602.7	0.165	1650	0.14	1	210	18	19	28	2	5	4.5	1.5	224	0.01
KL40-09	602.7	605.7	0.27	2700	0.27	1.4	49	18	160	42	2	3	22	1.5	190	0.01
KL40-09	605.7	608.7	0.198	1980	0.15	1.3	23	12	120	59	2	2	40	1.6	44	0.01
KL40-09	608.7	611.7	0.3	3000	0.14	1.8	156	56	45	184	3	7	14.9	3.8	61	0.01
KL40-09	611.7	614.7	0.194	1940	0.04	1.5	16	14	5	42	3	3	1.8	4.1	244	0.01
KL40-09	614.7	617.7	0.193	1930	0.05	1.1	32	23	25	27	3	3	2.2	3.8	68	0.01
KL40-09	617.7	620.7	0.21	2100	0.11	1.6	23	17	3	25	3	3	1.1	1.8	210	0.01
KL40-09	620.7	623.7	0.149	1490	0.12	1.6	36	25	4	20	3	4	1.1	1.6	218	0.01
KL40-09	623.7	626.7	0.177	1770	0.06	0.6	15	15	8	50	1	4	0.8	2.0	265	0.01
KL40-09	626.7	629.1	0.23	2300	0.15	1.5	190	152	44	395	1	6	14.5	4.0	126	0.01
KL40-09	629.1	632.7	0.23	2300	0.05	1.2	29	18	1	38	1	3	0.6	1.7	59	0.01
KL40-09	632.7	635.7	0.21	2100	0.06	1.3	133	14	1	99	1	7	0.6	2.7	240	0.01
KL40-09	635.7	638.7	0.168	1680	0.01	1.1	73	36	2	56	0.01	3	2	2.3	240	0.01
KL40-09	638.7	641.7	0.117	1170	0.04	1	54	30	5	119	5	5	3.2	3.5	220	0.01
KL40-09	641.7	644.7	0.168	1680	0.09	1.2	71	25	15	75	2	4	6.9	2.6	44	0.01
KL40-09	644.7	647.7	0.159	1590	0.03	0.8	34	17	7	36	1	10	1.4	4.4	232	0.01
KL40-09	647.7	650.7	0.141	1410	0.02	0.8	18	8	2	42	2	5	0.8	2.0	172	0.01
KL40-09	650.7	653.7	0.144	1440	0.01	0.9	22	9	0.01	169	1	5	0.3	1.7	266	0.01
KL40-09	653.7	656.9	0.122	1220	0.05	0.8	34	15	0.01	126	1	5	0.7	1.7	218	0.01
KL40-09	656.9	659.9	0.159	1590	0.04	1.4	261	257	0.01	161	6	3	1.3	2.3	298	0.01
KL40-09	659.9	662.9	0.165	1650	0.07	0.9	263	80	0.01	89	2	3	0.5	2.3	174	0.01
KL40-09	662.9	665.9	0.22	2200	0.03	0.9	53	25	1	39	1	4	0.01	2.8	184	0.01
KL40-09	665.9	668.9	0.172	1720	0.01	0.8	112	37	2	99	2	2	0.8	2.3	227	0.01
KL40-09	668.9	670	0.25	2500	0.03	1	267	54	9	160	1	3	1.3	3.5	42	0.01
KL40-09	670	673	0.322	3220	0.01	1.3	131	65	6	530	1	2	0.7	4.0	61	0.01
KL40-09	673	674.7	0.202	2020	0.11	0.9	257	78	0.01	39	0.01	4	0.01	3.0	50	0.01
KL40-09	674.7	677.7	0.27	2700	0.13	2.8	420	242	8	96	13	13	1.1	3.5	295	0.01
KL40-09	677.7	679.8	0.194	1940	0.03	1.5	292	116	2	68	2	2	0.2	2.0	243	0.01
KL40-09	679.8	682.9	0.197	1970	0.07	1.5	1210	353	0.01	44	1	5	0.6	2.2	37	0.01
KL40-09	682.9	685.9	0.22	2200	0.03	1.1	100	50	0.01	51	1	4	0.4	2.5	204	0.01
KL40-09	685.9	687.8	0.173	1730	0.02	1	237	100	0.01	150	0.01	4	0.4	4.5	150	0.01
KL40-09	687.8	689.7	0.142	1420	0.02	0.9	114	49	0.01	67	1	4	0.4	1.8	170	0.01
KL40-09	689.7	692.7	0.198	1980	0.03	1.5	32	16	0.01	109	1	4	0.3	2.8	177	0.01
KL40-09	692.7	695.7	0.178	1780	0.04	0.7	164	51	2	104	1	2	0.01	1.8	228	0.01
KL40-09	695.7	698.7	0.155	1550	0.02	0.6	125	58	2	165	0.01	2	0.6	1.0	73	0.01
KL40-09	698.7	701.7	0.198	1980	0.01	0.7	67	48	1	610	0.01	2	0.2	2.0	64	0.01
KL40-09	701.7	704.7	0.198	1980	0.01	1	108	66	1	289	0.01	1	0.5	2.3	214	0.01
KL40-09	704.7	707.7	0.181	1810	0.03	1.1	130	26	9	74	3	4	1.6	5.9	215	0.01
KL40-09	707.7	710.7	0.173	1730	0.2	0.8	136	143	57	91	2	10	1	4.3	56	0.01
KL40-09	710.7	713.7	0.135	1350	0.03	1.1	100	88	93	122	1	3	1.6	2.8	275	0.01
KL40-09	713.7	716.7	0.29	2900	0.07	1	138	86	30	70	2	2	2.5	3.5	33	0.01
KL40-09	716.7	718.7	0.276	2760	0.01	1.2	56	37	5	33	1	1	0.5	4.8	210	0.01
KL40-09	718.7	721.7	0.317	3170	0.01	1	72	41	2	31	1	2	0.9	3.3	213	0.01
KL40-09	721.7	724.5	0.23	2300	0.01	1.5	37	24	17	27	1	2	0.01	2.5	253	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL40-09	724.5	727.3	0.21	2100	0.01	1.4	50	20	11	22	0.01	2	0.7	2.3	203	0.01
KL40-09	727.3	728.7	0.284	2840	0.01	0.7	47	19	12	157	1	2	0.6	2.5	208	0.01
KL40-09	728.7	731.7	0.288	2880	0.01	1	51	31	3	129	0.01	2	0.6	2.8	205	0.01
KL40-09	731.7	734.7	0.271	2710	0.01	0.8	38	13	17	348	0.01	2	1.3	2.4	230	0.01
KL40-09	734.7	737.7	0.366	3660	0.06	1.1	47	14	5	46	1	4	0.8	3.0	154	0.01
KL40-09	737.7	740.7	0.21	2100	0.03	1	54	16	9	18	1	3	1.2	1.8	262	0.01
KL40-09	740.7	743.7	0.14	1400	0.08	0.9	28	13	13	125	0.01	6	1.4	2.8	180	0.01
KL40-09	743.7	746.7	0.148	1480	0.01	0.6	37	18	6	279	0.01	3	0.7	1.3	206	0.01
KL40-09	746.7	749.7	0.151	1510	0.01	0.6	47	23	3	45	0.01	3	0.4	1.8	198	0.01
KL40-09	749.7	752.7	0.123	1230	0.01	0.1	64	31	4	34	0.01	2	1	1.4	238	0.01
KL40-09	752.7	755.7	0.165	1650	0.02	0.8	74	40	1	15	0.01	3	0.01	1.5	192	0.01
KL40-09	755.7	758.6	0.365	3650	0.1	1	75	37	10	103	2	2	2.2	2.5	196	0.01
KL40-09	758.6	761.7	0.192	1920	0.02	0.6	41	14	1	97	0.01	3	0.3	1.5	210	0.01
KL40-09	761.7	764.7	1.15	11500	0.32	1.9	2500	16	4	14	3	38	0.3	9.8	134	0.01
KL40-09	764.7	767.7	0.143	1430	0.01	0.1	47	17	2	112	0.01	4	0.2	1.5	158	0.01
KL40-09	767.7	769.3	0.083	830	0.01	0.1	43	18	1	74	0.01	5	0.5	1.3	106	0.01
KL40-09	769.3	771.7	0.177	1770	0.01	0.1	63	25	2	60	0.01	3	0.3	1.0	206	0.01
KL40-09	771.7	773.7	0.075	750	0.01	0.6	34	26	13	63	0.01	1	2	2.0	197	0.01
KL40-09	773.7	776.7	0.169	1690	0.02	0.8	54	28	22	23	0.01	5	1.8	1.6	208	0.01
KL40-09	776.7	778.7	0.195	1950	0.01	0.7	40	20	4	46	0.01	1	0.6	1.3	241	0.01
KL40-09	778.7	780.5	0.178	1780	0.02	0.6	18	12	6	26	0.01	1	0.8	0.8	197	0.01
KL40-09	780.5	782.7	0.193	1930	0.01	0.1	95	42	11	23	0.01	1	3.8	0.5	188	0.01
KL42-01	0	3.3	0.0076	76	0.01	0.6	72	93	4	0.01	0.01	0.01	1.7	0.7	13	0.01
KL42-01	3.3	6.5	0.001	10	0.02	1.2	165	195	15	0.01	0.01	0.01	3.1	1.2	16	0.1
KL42-01	6.5	9.6	0.002	20	0.02	0.7	141	99	6	0.01	0.01	0.01	2.4	1.1	15	0.1
KL42-01	9.6	12	0.0007	7	0.01	0.01	189	69	10	0.01	0.01	0.01	1.3	0.9	48	0.01
KL42-01	12	13.9	0.0009	9	0.01	0.7	145	73	13	0.01	0.01	0.01	1.8	0.5	15	0.01
KL42-01	13.9	17.7	0.0011	11	0.01	0.6	94	65	9	0.01	0.01	0.01	1.7	0.8	16	0.01
KL42-01	17.7	19.8	0.0024	24	0.01	0.5	121	60	8	0.01	0.01	0.01	1.2	1.5	16	0.01
KL42-01	19.8	21.9	0.0011	11	0.01	0.01	133	48	9	2	0.01	0.01	1.3	1.6	15	0.01
KL42-01	21.9	24.2	0.0009	9	0.03	0.01	68	36	8	2	0.01	0.01	1.5	1.5	17	0.01
KL42-01	24.2	26.5	0.0009	9	0.02	0.01	63	27	6	0.01	0.01	0.01	1	1.5	21	0.01
KL42-01	26.5	29.5	0.0016	16	0.01	0.5	72	75	15	0.01	0.01	0.01	1.1	0.6	25	0.01
KL42-01	29.5	32.5	0.0007	7	0.04	0.01	70	32	5	0.01	0.01	0.01	1.8	1.0	35	0.12
KL42-01	32.5	35.4	0.0021	21	0.03	1.6	710	410	10	0.01	2	2	3.8	1.2	26	0.19
KL42-01	35.4	38.2	0.0022	22	0.02	1.4	640	650	9	0.01	0.01	0.01	2.5	1.3	35	0.13
KL42-01	38.2	41.5	0.001	10	0.01	0.7	86	48	24	2	0.01	0.01	3.9	1.9	24	0.1
KL42-01	41.5	45.3	0.0015	15	0.16	3.6	229	151	18	0.01	0.01	0.01	10	1.0	30	0.43
KL42-01	45.3	50.3	0.0011	11	0.2	2.4	181	113	15	0.01	0.01	0.01	4	1.1	26	0.18
KL42-01	50.3	51.8	0.003	30	0.03	2.2	830	760	11	0.01	2	0.01	2.2	2.3	22	0.01
KL42-01	51.8	54.9	0.0008	8	0.01	0.01	36	40	14	3	0.01	0.01	1.1	1.6	27	0.01
KL42-01	54.9	58	0.0013	13	0.01	0.01	22	22	15	2	0.01	0.01	0.7	1.0	45	0.01
KL42-01	58	59.6	0.0013	13	0.01	0.6	28	22	29	3	0.01	0.01	1.3	2.5	30	0.01
KL42-01	59.6	62.5	0.0008	8	0.02	0.5	44	47	18	2	0.01	0.01	0.9	2.1	19	0.01
KL42-01	62.5	65.5	0.0007	7	0.03	0.01	39	41	13	0.01	0.01	0.01	1.2	1.5	18	0.01
KL42-01	65.5	67.9	0.001	10	0.07	0.8	85	72	19	2	0.01	0.01	4.1	1.7	23	0.01
KL42-01	67.9	71	0.0032	32	0.02	0.6	39	39	17	4	0.01	2	3.9	1.6	26	0.01
KL42-01	71	73.6	0.0164	164	0.02	4.6	298	237	39	3	0.01	0.01	4.8	7.8	20	0.01
KL42-01	73.6	75	0.0026	26	0.01	1.5	199	460	12	2	0.01	0.01	9.3	3.0	20	0.14
KL42-01	75	77.5	0.0035	35	0.2	2.6	195	480	32	3	0.01	2	23	2.2	32	0.15
KL42-01	77.5	80.5	0.001	10	0.14	1.1	70	188	22	0.01	0.01	0.01	12	1.8	25	0.1
KL42-01	80.5	83.5	0.0011	11	0.02	0.9	66	74	7	0.01	0.01	0.01	1.8	2.4	20	0.01
KL42-01	83.5	86.5	0.001	10	0.07	0.7	58	53	9	0.01	0.01	0.01	3.1	1.3	30	0.11
KL42-01	86.5	89.5	0.0022	22	0.04	1.5	251	155	9	4	2	0.01	2.6	2.1	24	0.01
KL42-01	89.5	92.5	0.001	10	0.03	1.1	241	206	11	0.01	0.01	0.01	1.8	2.2	24	0.1
KL42-01	92.5	96	0.0013	13	0.1	1.3	308	500	19	2	0.01	2	4.8	6.3	31	0.22
KL42-01	96	98.3	0.0016	16	0.04	1.1	50	214	19	0.01	0.01	0.01	4.9	5.8	25	0.01
KL42-01	98.3	101.4	0.0035	35	0.06	1.5	169	232	21	0.01	0.01	0.01	18	4.7	23	0.2
KL42-01	101.4	104.5	0.0011	11	0.05	0.01	61	116	15	0.01	0.01	0.01	4.5	1.9	22	0.01
KL42-01	104.5	107.5	0.001	10	0.09	0.7	64	154	17	3	0.01	0.01	6.7	1.5	19	0.01
KL42-01	107.5	110.1	0.0026	26	0.09	1.2	142	520	39	4	0.01	0.01	35	4.9	22	0.11
KL42-01	110.1	113.2	0.001	10	0.09	0.8	101	89	11	2	0.01	0.01	3.2	2.5	18	0.1
KL42-01	113.2	115.8	0.0068	68	0.16	0.6	91	65	21	5	0.01	0.01	2.6	2.0	21	0.1

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL42-01	115.8	116.9	0.0039		39	0.07	0.01	99	98	18	3	0.01	0.01	3.8	3.5	20	0.01
KL42-01	116.9	119.5	0.0049		49	0.08	0.8	103	217	34	6	0.01	0.01	2.7	4.1	26	0.12
KL42-01	119.5	122.5	0.0047		47	0.08	1.3	129	291	61	8	3	0.01	4.4	5.7	34	0.01
KL42-01	122.5	124.8	0.0163		163	0.14	2.1	208	470	50	15	4	0.01	4	9.7	32	0.21
KL42-01	124.8	127.1	0.0176		176	0.06	2.4	1700	435	49	19	6	0.01	7.6	6.4	29	0.29
KL42-01	127.1	129.9	0.0236		236	0.04	2.4	2420	307	65	40	6	2	8.2	4.9	36	0.3
KL42-01	129.9	132.5	0.0526		526	0.13	5.3	3400	692	160	99	10	3	7.4	9.1	31	0.35
KL42-01	132.5	134.5	0.0199		199	0.05	1.7	920	275	67	60	5	0.01	4.4	2.8	37	0.13
KL42-01	134.5	136.3	0.0054		54	0.1	0.7	365	224	160	146	2	4	9.5	4.1	78	0.16
KL42-01	136.3	139.3	0.0064		64	0.12	0.9	900	351	180	730	6	4	12.4	5.6	57	0.23
KL42-01	139.3	142.5	0.129		1290	0.46	12.5	6100	1930	120	620	73	5	31	28.5	33	0.17
KL42-01	142.5	145.6	0.0293		293	0.22	9.6	2540	7100	230	430	28	0.01	15.1	18.8	30	0.11
KL42-01	145.6	148.7	0.0306		306	0.09	9.3	2660	1030	100	95	25	2	11.1	27.2	34	0.01
KL42-01	148.7	150.7	0.0105		105	1.04	5.3	4920	267	680	920	103	3	52	31.5	54	0.54
KL42-01	150.7	154.8	0.0064		64	0.49	1.5	1700	201	380	740	26	3	62	9.5	128	0.21
KL42-01	154.8	156.8	0.0044		44	1.04	4.7	2010	331	580	23	71	2	19	33.0	44	0.1
KL42-01	156.8	159.4	0.0205		205	0.6	25.2	4780	1670	480	114	209	9	29	124.0	96	0.01
KL42-01	159.4	161.5	0.101		1010	0.23	6.4	8000	540	130	24	31	10	5.5	47.0	58	0.01
KL42-01	161.5	164.1	0.096		960	0.32	6.8	10300	580	74	132	30	19	17.2	20.8	54	0.1
KL42-01	164.1	167.5	0.1		1000	0.2	3.2	421	88	60	396	5	4	1.8	4.5	32	0.1
KL42-01	167.5	170.5	0.047		470	0.14	4	9300	335	130	117	10	16	2.8	12.0	50	0.1
KL42-01	170.5	172.7	0.36		3600	1.33	53	49900	5200	1310	157	253	61	18	390.0	54	0.01
KL42-01	172.7	173.9	0.52		5200	0.43	40	77000	3600	400	170	81	80	14.5	80.0	38	0.76
KL42-01	173.9	176.3	0.66		6600	0.58	17.1	19600	640	290	750	48	50	10.9	68.0	67	0.34
KL42-01	176.3	179.4	0.62		6200	0.77	23	23400	2700	300	274	50	50	12	38.0	86	1.02
KL42-01	179.4	182.1	0.6		6000	2.27	26.2	16700	2900	620	996	75	38	24	34.5	63	1.56
KL42-01	182.1	184.6	0.57		5700	1.24	15.7	29100	760	470	457	20	30	15.3	35.0	30	0.49
KL42-01	184.6	187.6	0.128		1280	0.14	3.5	2910	365	58	216	9	5	3.7	13.0	40	0.1
KL42-01	187.6	190.9	0.155		1550	0.21	5	6000	1080	67	420	16	7	4.1	13.8	27	0.01
KL42-01	190.9	194	0.0558		558	0.16	4.2	4100	1950	83	345	18	2	4.4	11.5	20	0.18
KL42-01	194	197.1	0.131		1310	0.41	11.9	18600	6200	250	762	111	5	8.4	92.0	28	0.19
KL42-01	197.1	200.2	0.157		1570	0.94	18	7500	5400	200	876	90	6	10.5	48.0	23	0.1
KL42-01	200.2	203.3	0.14		1400	1.06	15	4480	9500	190	710	54	4	11.3	35.0	26	0.11
KL42-01	203.3	206.4	0.0377		377	0.31	25.3	17600	23500	170	369	62	0.01	14.5	55.0	22	0.1
KL42-01	206.4	209.3	0.0374		374	0.43	17.3	5700	15100	340	451	46	0.01	20	50.0	24	0.17
KL42-01	209.3	212.3	0.0319		319	0.2	18.9	15100	17200	100	261	47	2	11.2	36.0	20	0.11
KL42-01	212.3	214.7	0.0323		323	0.26	24.9	15000	14400	150	203	44	0.01	17.4	26.0	21	0.27
KL42-01	214.7	216	0.0403		403	0.38	47	24700	27500	180	261	82	0.01	26	57.0	21	0.68
KL42-01	216	219	0.047		470	0.33	26.7	16100	16600	160	269	18	3	31	23.9	23	0.62
KL42-01	219	221.5	0.0339		339	0.28	8	6400	4000	120	177	18	2	9.6	15.8	22	0.35
KL42-01	221.5	224.5	0.0312		312	1.14	13.1	5000	3300	65	213	22	2	8.1	12.5	22	0.27
KL42-01	224.5	227.5	0.075		750	0.39	35	7000	5100	220	272	55	3	17.4	28.8	28	0.31
KL42-01	227.5	229.9	0.058		580	0.2	3.7	2200	475	100	174	32	2	5.8	11.8	23	0.01
KL42-01	229.9	232.9	0.0108		108	0.05	2	410	309	34	80	5	0.01	1.7	4.5	23	0.01
KL42-01	232.9	234.8	0.0185		185	0.12	1.6	880	221	56	163	18	0.01	3.5	9.5	20	0.01
KL42-01	234.8	238	0.0194		194	0.24	2.7	1850	640	140	188	20	0.01	6.4	17.2	24	0.01
KL42-01	238	240.7	0.0325		325	0.44	4.5	3500	2120	180	210	20	0.01	15.8	23.8	25	0.2
KL42-01	240.7	241.9	0.0252		252	0.19	2.8	2800	880	65	152	17	0.01	4.5	15.8	22	0.01
KL42-01	241.9	245.2	0.0267		267	0.46	7.1	3930	2400	57	163	25	0.01	5	21.8	22	0.01
KL42-01	245.2	248.5	0.0269		269	0.36	3.9	3210	1100	250	128	24	0.01	9.2	22.5	24	0.01
KL42-01	248.5	251	0.082		820	0.85	23.3	9400	4300	340	972	56	4	17.1	55.0	35	0.19
KL42-01	251	252.4	0.0237		237	0.11	3	1070	420	52	104	11	2	2.7	11.5	22	0.01
KL42-01	252.4	255.4	0.0297		297	0.08	3.3	1310	920	36	84	8	2	2.6	14.5	27	0.01
KL42-01	255.4	258	0.053		530	0.05	6.3	5300	9400	130	59	6	0.01	4.3	11.0	24	0.01
KL42-01	258	260.1	0.0092		92	0.04	0.9	480	378	20	31	2	0.01	1.2	2.9	21	0.01
KL42-01	260.1	262.4	0.0119		119	0.03	0.01	386	49	9	37	4	0.01	0.7	2.3	24	0.01
KL42-01	262.4	265.1	0.209		2090	0.17	12.6	10700	2100	66	166	30	19	4.9	27.8	44	0.01
KL42-01	265.1	267.5	0.0123		123	0.03	0.8	440	175	17	16	0.01	0.01	0.9	2.3	22	0.01
KL42-01	267.5	270.5	0.009		90	0.07	0.7	132	127	12	42	3	0.01	0.6	4.0	25	0.01
KL42-01	270.5	273.1	0.02		200	0.06	1.2	660	394	16	42	1	0.01	1.2	5.0	24	0.01
KL42-01	273.1	276	0.075		750	0.15	5.9	3530	480	100	150	18	6	3.6	15.5	35	0.01
KL42-01	276	279.9	0.144		1440	0.21	10.3	6400	1210	180	153	38	12	9.9	18.2	44	0.21
KL42-01	279.9	281.3	0.0119		119	0.13	2.2	980	2430	25	283	1	0.01	3.3	6.2	29	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL42-01	281.3	284.9	0.161		1610	0.17	10.3	9800	860	110	83	33	16	6.4	22.7	49	0.01
KL42-01	284.9	286.9	0.0113		113	0.06	0.01	241	261	14	152	2	0.01	1.1	6.2	15	0.01
KL42-01	286.9	290	0.0081		81	0.08	3.8	650	740	22	100	27	0.01	1.2	34.2	16	0.01
KL42-01	290	292.6	0.083		830	0.1	1.5	1090	75	79	291	6	0.01	2.9	5.0	18	0.11
KL42-01	292.6	294.9	0.0162		162	0.2	3.2	1630	960	41	83	10	0.01	3.6	14.8	28	0.11
KL42-01	294.9	297.2	0.0162		162	0.2	3.2	1630	960	41	83	10	0.01	3.6	14.8	28	0.11
KL42-01	297.2	302	0.102		1020	0.16	4.7	5800	1040	120	62	24	8	14.8	23.8	27	0.1
KL42-01	302	303.9	2.25		22500	4.56	28.9	4300	930	500	362	6	64	26	27.0	34	1.18
KL42-01	303.9	305.4	4.39		43900	2.12	39	28800	910	160	584	104	129	6.1	39.5	16	0.17
KL42-01	305.4	308.4	0.01		100	0.19	1.2	281	56	34	24	7	0.01	3.2	15.0	23	0.01
KL42-01	308.4	311.5	0.1		1000	0.2	5.3	6600	510	110	78	40	11	5.9	19.2	31	0.01
KL42-01	311.5	312.6	0.079		790	0.83	7.8	4320	750	120	24	28	17	9.4	30.0	32	0.01
KL42-01	312.6	314.5	0.0271		271	0.15	1.7	760	202	38	63	2	2	2.4	6.4	30	0.01
KL42-01	314.5	317.5	0.0089		89	0.14	0.01	170	117	24	75	0.01	0.01	1.4	3.5	16	0.01
KL42-01	317.5	320.6	0.11		1100	0.08	3.8	2460	880	100	33	25	4	3.8	26.0	28	0.01
KL42-01	320.6	322.3	0.0397		397	0.24	1.1	510	420	61	21	1	2	3.8	11.0	23	0.01
KL42-01	322.3	324.9	0.0025		25	0.02	0.01	236	216	20	5	0.01	0.01	1.3	3.5	18	0.01
KL42-01	324.9	328	0.0057		57	0.1	2.8	2070	2400	36	11	1	0.01	4.8	40.0	26	0.01
KL42-01	328	329.5	0.0228		228	0.17	8.7	1720	1350	63	13	26	3	4.7	21.2	35	0.01
KL42-01	329.5	332.5	0.0046		46	0.24	0.01	520	388	57	10	0.01	0.01	3.8	7.4	24	0.01
KL42-01	332.5	335.5	0.015		150	0.08	0.5	220	140	21	8	0.01	0.01	1.1	3.5	14	0.01
KL42-01	335.5	337.6	0.004		40	0.03	0.01	95	214	14	2	0.01	0.01	0.9	2.1	16	0.01
KL42-01	337.6	340.4	0.0059		59	0.02	0.01	159	99	15	0.01	0.01	0.01	0.4	1.8	13	0.01
KL42-01	340.4	343.5	0.0051		51	0.03	0.01	71	74	21	0.01	0.01	0.01	0.7	2.0	16	0.01
KL42-02	0	2.6	0.0018		18	0.01	1	102	108	3	2	0.01	0.01	1.9	1.0	24	0.01
KL42-02	2.6	5.6	0.0024		24	0.01	0.01	131	69	7	4	0.01	0.01	2.7	1.0	18	0.01
KL42-02	5.6	8.7	0.0036		36	0.01	0.01	139	74	14	0.01	0.01	0.01	2.6	1.8	20	0.01
KL42-02	8.7	11.6	0.005		50	0.01	0.7	211	98	9	5	0.01	0.01	2.1	2.0	21	0.01
KL42-02	11.6	14.2	0.0029		29	0.01	0.5	55	25	13	0.01	0.01	0.01	1.7	1.0	15	0.01
KL42-02	14.2	16.8	0.004		40	0.04	0.01	92	29	9	0.01	0.01	0.01	1.7	1.8	18	0.01
KL42-02	16.8	20.2	0.0029		29	0.07	0.01	93	27	9	0.01	0.01	0.01	1.6	1.0	32	0.01
KL42-02	20.2	23.6	0.0037		37	0.01	0.01	47	22	7	0.01	0.01	0.01	0.7	0.8	34	0.01
KL42-02	23.6	26.3	0.0023		23	0.01	0.01	26	22	9	0.01	0.01	0.01	0.7	1.2	29	0.01
KL42-02	26.3	29.4	0.0019		19	0.01	0.8	71	86	8	0.01	0.01	0.01	3.4	0.0	21	0.01
KL42-02	29.4	32.2	0.0017		17	0.08	2.8	1320	311	12	2	0.01	0.01	5.6	1.5	48	0.38
KL42-02	32.2	33.6	0.0062		62	0.1	1.1	158	127	13	2	0.01	0.01	2.9	1.2	29	0.11
KL42-02	33.6	35.6	0.0009		9	0.01	1.5	139	151	17	0.01	0.01	0.01	2.6	1.2	19	0.01
KL42-02	35.6	38.6	0.0025		25	0.01	1.4	97	172	10	2	0.01	0.01	1.1	1.2	14	0.01
KL42-02	38.6	41.6	0.005		50	0.01	2.5	198	336	16	7	0.01	2	1.5	1.5	18	0.01
KL42-02	41.6	44.6	0.0076		76	0.01	1.5	134	146	14	15	0.01	0.01	2.8	2.2	24	0.01
KL42-02	44.6	47.6	0.021		210	0.01	1.9	85	75	24	3	0.01	2	3.7	1.8	16	0.01
KL42-02	47.6	50.6	0.0082		82	0.01	0.01	75	42	10	10	0.01	2	0.7	1.2	21	0.01
KL42-02	50.6	53	0.0078		78	0.01	0.01	45	33	10	6	0.01	0.01	0.8	1.8	20	0.01
KL42-02	53	56.1	0.0035		35	0.01	0.7	131	70	8	3	0.01	0.01	2	1.5	18	0.01
KL42-02	56.1	57.9	0.0062		62	0.01	1.1	331	198	10	2	0.01	3	3.3	3.5	18	0.01
KL42-02	57.9	59.6	0.51		5100	0.86	10.7	4900	840	1980	1440	42	7	7.6	10.5	16	0.23
KL42-02	59.6	62.6	0.0044		44	0.12	0.01	60	17	24	10	0.01	3	1	1.9	18	0.01
KL42-02	62.6	65.6	0.0039		39	0.47	0.6	212	29	32	2	0.01	0.01	2.5	2.2	24	0.01
KL42-02	65.6	68	0.0019		19	0.07	0.01	73	38	11	3	0.01	3	1.8	3.0	14	0.01
KL42-02	68	70.1	0.3		3000	1.15	7	7900	360	860	115	43	8	6.9	10.8	30	0.3
KL42-02	70.1	71.6	0.0142		142	0.04	0.01	67	68	33	5	0.01	0.01	1.6	1.7	21	0.01
KL42-02	71.6	74.6	0.0165		165	0.16	1.4	500	520	120	0.01	0.01	0.01	28	8.8	23	0.16
KL42-02	74.6	77.6	0.0046		46	0.1	0.01	350	181	55	36	0.01	3	10.1	4.8	34	0.01
KL42-02	77.6	79.6	0.0096		96	0.07	0.6	425	127	46	48	0.01	0.01	6.2	3.5	24	0.01
KL42-02	79.6	81.6	0.009		90	0.1	0.5	228	115	57	10	1	4	7.5	5.5	18	0.01
KL42-02	81.6	83.6	0.073		730	0.19	31.7	7600	12000	210	58	62	6	140	259.0	62	0.49
KL42-02	83.6	86.2	0.0073		73	0.63	2.1	720	207	260	197	2	3	24	8.5	41	0.27
KL42-02	86.2	88.2	0.014		140	0.43	4.3	870	362	290	159	2	4	20	8.0	45	0.24
KL42-02	88.2	90.9	0.0238		238	0.54	2.1	550	217	290	350	3	4	18	8.5	61	0.36
KL42-02	90.9	93.8	0.045		450	0.23	3.5	1810	1070	200	894	3	3	46	13.5	65	0.24
KL42-02	93.8	96.6	0.46		4600	0.84	2	103	157	1370	2080	2	6	214	12.2	195	0.16
KL42-02	96.6	99.6	2.76		27600	1.31	1.5	680	420	450	2880	1	5	253	6.0	154	0.28
KL42-02	99.6	100.8	1.45		14500	1.37	0.9	202	138	180	2860	1	5	42	3.5	145	0.26

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL42-02	100.8	103	0.39	3900	0.64	1.2	90	37	700	90	0.01	0.01	92	2.5	92	0.1
KL42-02	103	104.5	0.0061	61	0.01	0.01	40	8	2	2	0.01	20	0.01	0.0	35	0.01
KL42-02	104.5	107.5	0.41	4100	0.8	3.8	96	103	630	447	2	3	82	12.8	140	0.34
KL42-02	107.5	109.9	0.16	1600	1.64	20.1	164	7600	340	1780	8	4	37	44.5	167	0.66
KL42-02	109.9	112.1	0.0161	161	1.04	10.5	3900	17000	160	520	4	3	16.8	19.2	176	0.55
KL42-02	112.1	113.6	0.046	460	0.55	21.9	5200	3000	230	3365	74	8	41	90.0	38	0.28
KL42-02	113.6	116.6	0.092	920	0.64	16.9	14600	3700	300	3800	154	7	124	76.0	81	0.68
KL42-02	116.6	119.6	0.087	870	1.83	14.5	5800	1920	1010	9750	62	10	102	51.0	101	1.17
KL42-02	119.6	122.6	0.112	1120	0.99	9.8	16000	1370	400	1930	42	9	65	82.0	35	0.96
KL42-02	122.6	125.6	0.0127	127	0.46	2.8	1680	1470	150	345	4	3	22	12.0	61	0.26
KL42-02	125.6	128.8	0.0152	152	0.67	4.9	3100	1180	410	220	9	3	16.8	8.2	21	0.39
KL42-02	128.8	131.7	0.0391	391	0.97	9.6	5500	2900	180	145	28	5	16.9	15.8	26	0.38
KL42-02	131.7	134.6	0.0124	124	0.86	2.3	3400	1500	100	156	5	2	6.7	5.5	25	0.34
KL42-02	134.6	137.7	0.0212	212	0.24	4	2310	2070	99	238	9	0.01	8.9	9.5	29	0.28
KL42-02	137.7	140	0.0086	86	0.11	1.7	1090	590	39	291	5	3	3.2	5.0	25	0.01
KL42-02	140	143	0.0041	41	0.12	0.8	480	352	31	152	3	2	2.5	2.8	24	0.01
KL42-02	143	145.4	0.0093	93	0.24	2.2	440	334	39	86	23	0.01	3.8	5.2	27	0.01
KL42-02	145.4	147.3	0.0168	168	0.1	8	3140	3700	37	47	17	2	3.4	31.0	22	0.01
KL42-02	147.3	150	0.0046	46	0.06	0.5	249	156	28	234	2	2	2.2	3.5	24	0.01
KL42-02	150	153.5	0.0389	389	0.24	1.5	1860	231	110	266	4	5	35	5.5	32	0.14
KL42-02	153.5	155.7	0.07	700	0.47	7.1	3850	1230	230	830	21	0.01	25	13.2	33	0.51
KL42-02	155.7	158.4	0.0148	148	0.17	2.9	2180	560	81	94	6	0.01	3.2	7.0	27	0.1
KL42-02	158.4	161.4	0.0204	204	0.3	4.6	2280	630	98	98	10	0.01	4.9	6.5	24	0.01
KL42-02	161.4	164.2	0.086	860	0.28	7.8	4200	1840	58	84	20	3	2.7	11.0	23	0.01
KL42-02	164.2	167.3	0.0181	181	0.12	2.3	1940	364	35	66	7	0.01	1.2	6.8	18	0.1
KL42-02	167.3	169.9	0.05	500	0.14	4.6	4350	730	82	90	18	0.01	1.3	8.5	12	0.01
KL42-02	169.9	172	0.0258	258	0.12	1.6	1940	110	63	63	6	0.01	0.7	4.2	14	0.01
KL42-02	172	174.2	0.078	780	0.25	3.2	2850	284	260	256	20	0.01	2	9.5	15	0.01
KL42-02	174.2	175.6	0.066	660	0.23	4.3	8300	383	110	200	22	2	1.7	9.8	18	0.26
KL42-02	175.6	177.8	0.0056	56	0.09	0.01	180	40	23	19	0.01	0.01	2.6	3.0	31	0.01
KL42-02	177.8	179.6	0.48	4800	1.37	10.7	6200	560	2010	506	34	8	10.8	11.8	49	0.42
KL42-02	179.6	182	0.46	4600	2.13	18.4	8800	780	1380	2240	99	11	9.5	27.5	40	0.32
KL42-02	182	185.2	0.47	4700	2.35	14.4	12500	4900	1120	800	39	9	13.8	14.8	32	0.42
KL42-02	185.2	188.2	0.0065	65	0.1	0.01	186	50	42	20	0.01	0.01	1.5	2.0	29	0.01
KL42-02	188.2	191.3	0.14	1400	0.76	7.9	15300	550	400	34	43	3	4	8.5	38	0.12
KL42-02	191.3	194.4	1.26	12600	1.88	24.3	12000	650	1020	415	57	24	5.2	18.5	73	0.01
KL42-02	194.4	197.6	0.46	4600	1.85	9.8	16300	120	190	84	40	41	4.3	19.5	57	0.01
KL42-02	197.6	200.6	0.74	7400	1.92	16	17500	83	120	81	27	21	4.7	17.5	48	0.01
KL42-02	200.6	203.6	0.85	8500	1.37	12.1	7200	2800	120	155	21	24	5.5	28.0	55	0.01
KL42-02	203.6	206.3	0.77	7700	1.52	11.1	570	62	310	56	15	15	7.3	12.2	76	0.01
KL42-02	206.3	209	1.45	14500	2.38	17.6	640	172	410	36	112	25	8.2	18.5	59	0.01
KL42-02	209	212.1	1.49	14900	1.52	16.1	1540	1900	210	1250	8	20	4.9	28.0	76	0.01
KL42-02	212.1	213.5	0.76	7600	0.52	6.1	6900	5900	67	153	3	31	4.8	33.0	130	0.01
KL42-02	213.5	215	0.0144	144	0.01	0.01	13	7	3	7	0.01	2	0.01	0.0	112	0.01
KL42-02	215	217.6	0.38	3800	0.19	2.9	620	420	16	880	4	35	1	20.6	96	0.01
KL42-02	217.6	219.5	1.31	13100	0.34	17.5	6000	2100	160	659	7	82	14.5	48.0	69	0.13
KL42-02	219.5	221.6	0.91	9100	0.14	12.7	1670	1160	100	760	3	82	2.8	46.0	182	0.01
KL42-02	221.6	224.6	0.59	5900	0.31	5.5	570	2100	100	540	25	60	1.9	47.5	164	0.12
KL42-02	224.6	227.6	1.46	14600	0.32	13.6	950	2100	43	420	5	70	2.8	18.5	106	0.12
KL42-02	227.6	230.6	0.34	3400	0.15	7.1	400	2310	25	511	3	38	2.7	17.0	95	0.01
KL42-02	230.6	233.6	0.56	5600	0.18	5.6	284	630	26	304	5	44	2	12.5	42	0.01
KL42-02	233.6	236.6	0.86	8600	0.17	6.1	337	281	18	1100	4	46	1.4	11.2	50	0.01
KL42-02	236.6	239.6	0.84	8400	0.14	6.7	810	700	21	830	6	41	1.6	11.5	69	0.01
KL42-02	239.6	242.5	0.74	7400	0.15	5.6	680	640	45	288	3	39	2.4	7.8	87	0.01
KL42-02	242.5	245.1	0.76	7600	0.16	5.8	520	690	38	376	4	42	1.6	48.5	104	0.01
KL42-02	245.1	248.2	0.44	4400	0.18	6.8	870	900	140	178	10	40	9.3	16.0	114	0.12
KL42-02	248.2	251.2	0.35	3500	0.23	6.7	640	3000	50	540	6	29	5.2	11.8	79	0.01
KL42-02	251.2	254.2	0.156	1560	0.14	4.2	710	1470	38	152	3	20	2.8	11.5	70	0.01
KL42-02	254.2	257.2	0.39	3900	0.24	4.6	460	780	64	120	3	17	4	8.0	105	0.01
KL42-02	257.2	259.1	0.78	7800	0.49	4.1	500	220	61	156	1	30	1.8	8.5	113	0.01
KL42-02	259.1	260.6	0.56	5600	0.38	4.2	540	302	79	144	4	19	1.3	6.5	69	0.01
KL42-02	260.6	263.6	0.71	7100	0.45	5.2	1000	540	54	305	2	40	1.5	8.8	76	0.01
KL42-02	263.6	266.6	0.7	7000	0.4	3.1	371	129	42	198	1	29	1.3	8.2	70	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL42-02	266.6	269.1	0.74	7400	0.42	4.5	430	800	49	471	2	17	1.4	9.2	49	0.01
KL42-02	269.1	272.1	1.14	11400	0.64	5.4	560	500	31	63	2	29	1.5	10.2	72	0.01
KL42-02	272.1	274.2	0.65	6500	0.36	4.7	900	590	46	193	3	13	4.3	10.5	75	0.01
KL42-02	274.2	276.3	0.92	9200	0.56	2.7	570	182	21	78	2	15	1.2	11.2	30	0.01
KL42-02	276.3	278.6	0.87	8700	0.58	3.4	650	326	64	51	4	29	2.3	9.8	49	0.01
KL42-02	278.6	281.6	0.41	4100	0.26	2.7	520	364	39	168	2	43	2	15.2	112	0.01
KL42-02	281.6	284.6	0.52	5200	0.21	2.7	270	1130	26	49	2	28	1.3	9.8	61	0.01
KL42-02	284.6	286.3	0.61	6100	0.39	3.6	276	122	31	49	6	24	0.8	13.6	32	0.01
KL42-02	286.3	288.8	0.95	9500	0.37	3.5	1070	374	70	255	2	27	1.2	12.5	53	0.01
KL42-02	288.8	290.6	1.39	13900	0.47	7.7	330	145	44	184	2	31	0.8	20.5	68	0.01
KL42-02	290.6	293.6	0.44	4400	0.21	2.4	255	87	33	165	2	20	0.8	13.5	58	0.01
KL42-02	293.6	296.6	1.1	11000	0.4	6.3	416	98	34	226	2	32	1.6	17.5	50	0.01
KL42-02	296.6	299.6	1.3	13000	0.64	4.5	840	307	79	125	2	47	2.6	16.5	55	0.01
KL42-02	299.6	302.6	2.93	29300	2.06	9.8	650	156	200	278	8	64	2.9	27.0	76	0.01
KL42-02	302.6	305.6	2.92	29200	1.28	10.5	750	234	250	151	8	41	2.7	28.0	92	0.01
KL42-02	305.6	308.6	1.17	11700	0.64	4	252	73	22	98	3	31	0.9	28.0	60	0.01
KL42-02	308.6	311.6	1.58	15800	1.52	7.5	650	299	58	75	2	20	0.9	11.5	61	0.01
KL42-02	311.6	313.5	1.04	10400	0.82	7.1	1410	2500	130	65	7	36	2.2	26.0	73	0.01
KL42-02	313.5	314.6	4.42	44200	3.44	10.8	1410	740	74	27	3	36	2.3	29.5	79	0.01
KL42-02	314.6	317.6	6.61	66100	4.29	7.3	1660	223	22	31	1	45	3	50.0	40	0.01
KL42-02	317.6	320.6	4.89	48900	3.33	7.4	910	125	52	33	1	59	3.6	44.0	46	0.01
KL42-02	320.6	323.6	4.25	42500	3.12	7.1	970	141	41	118	1	62	3.4	22.0	63	0.01
KL42-02	323.6	326.6	3.91	39100	2.48	4.5	480	77	6	19	0.01	45	1.3	20.0	46	0.01
KL42-02	326.6	329.6	3	30000	1.81	3.7	690	137	7	74	1	56	1.4	20.0	57	0.01
KL42-02	329.6	332.6	3.4	34000	2.4	4.7	940	600	6	109	1	57	1.5	23.0	43	0.01
KL42-02	332.6	335.6	2.61	26100	1.96	5.3	710	540	8	34	2	51	1.9	20.0	41	0.01
KL42-02	335.6	338.6	2.6	26000	1.76	4.9	640	72	9	33	1	57	1.1	20.0	54	0.01
KL42-02	338.6	341.6	3.41	34100	2.12	4.8	810	52	7	11	2	54	1	15.0	48	0.01
KL42-02	341.6	344.6	2.62	26200	1.71	4.9	810	75	7	17	3	43	1.1	19.0	45	0.01
KL42-02	344.6	347.6	3.05	30500	2.27	11.4	720	84	16	66	4	57	1.7	27.0	56	0.01
KL42-02	347.6	350.6	2.98	29800	1.86	6.9	460	61	14	28	3	57	1.2	28.0	46	0.01
KL42-02	350.6	353.6	3.36	33600	2.03	6.5	950	85	4	42	1	46	1.8	15.0	49	0.01
KL42-02	353.6	356.6	2.59	25900	1.66	4.7	840	136	5	28	3	46	1.1	13.0	41	0.01
KL42-02	356.6	359.6	2.64	26400	1.95	4.5	900	86	5	25	3	47	1.6	13.0	56	0.01
KL42-02	359.6	362.6	3.02	30200	2.03	8.9	820	200	24	43	9	57	1.6	26.0	48	0.01
KL42-02	362.6	365.6	7.06	70600	3.84	12.4	860	124	34	131	4	51	0.8	41.2	76	0.01
KL42-02	365.6	368.6	3.88	38800	2.83	7.1	1130	79	5	21	2	56	0.8	17.0	48	0.01
KL42-02	368.6	371.6	4.75	47500	4.16	6.4	1100	167	22	78	1	52	1	35.0	57	0.01
KL42-02	371.6	374.6	2.23	22300	1.92	4.1	1390	363	13	45	1	40	1.8	15.5	79	0.01
KL42-02	374.6	377.6	3.55	35500	2.27	4.8	1120	107	4	47	1	34	1.3	18.0	54	0.01
KL42-02	377.6	380	4.02	40200	2.51	6	1360	176	16	169	1	48	1.5	28.5	69	0.01
KL42-02	380	382	3.32	33200	2.32	10.4	770	157	30	229	6	41	1.1	31.0	84	0.01
KL42-02	382	385	14.4	144000	6.16	14.7	359	176	84	98	4	20	6.2	27.5	76	0.2
KL42-02	385	386.7	2.68	26800	2.27	8.5	1530	420	24	60	8	44	2	28.0	104	0.01
KL42-02	386.7	388.3	3.01	30100	2	7.9	1070	208	27	37	6	37	2	27.5	84	0.01
KL42-02	388.3	389.5	7.1	71000	3.12	19.8	5200	490	32	167	2	47	1.9	27.5	83	0.01
KL42-02	389.5	392.2	2.91	29100	1.87	13.2	810	189	23	18	25	44	2.1	18.0	76	0.01
KL42-02	392.2	395.2	4.78	47800	2.5	17.1	3000	334	44	99	4	50	1.7	27.5	63	0.01
KL42-02	395.2	398.3	1.49	14900	1.78	9.6	770	369	33	68	13	32	0.7	23.5	98	0.01
KL42-02	398.3	401.4	1	10000	1.68	7.6	3300	2100	49	96	24	14	0.7	17.0	145	0.01
KL42-02	401.4	404.5	1.61	16100	2.03	11.2	2600	1140	40	99	24	35	0.7	25.0	95	0.01
KL42-02	404.5	407.5	0.89	8900	1.68	5.3	760	225	25	12	14	54	1.2	19.0	83	0.01
KL42-02	407.5	410.5	1.84	18400	2.05	12.1	1840	414	26	78	19	38	0.9	39.0	74	0.01
KL42-02	410.5	413.5	1.41	14100	1.71	13.7	1530	192	21	27	36	81	1	33.2	56	0.01
KL42-02	413.5	416.5	1.89	18900	2.56	18.2	1100	168	8	129	32	80	1.5	15.0	68	0.01
KL42-02	416.5	419.5	2.29	22900	2.24	27.3	2300	610	11	26	28	42	1.2	20.0	98	0.01
KL42-02	419.5	422.5	2.34	23400	1.9	44	780	167	15	52	7	47	1.6	18.0	68	0.01
KL42-02	422.5	425.5	4.14	41400	4.38	46	610	129	10	29	5	50	1.6	30.0	51	0.01
KL42-02	425.5	428.5	3.33	33300	2.02	6.2	430	106	44	104	7	41	1.3	27.0	88	0.01
KL42-02	428.5	431.5	1.62	16200	0.68	3.7	278	95	140	425	8	31	0.7	23.0	98	0.01
KL42-02	431.5	434.5	1.69	16900	0.91	3.9	1200	157	43	291	6	34	1	26.8	101	0.01
KL42-02	434.5	437.5	1.85	18500	0.52	7.5	2400	2000	54	288	6	23	1.7	19.0	84	0.01
KL42-02	437.5	439.4	2.23	22300	0.37	4.1	580	102	49	585	5	15	0.6	18.0	106	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL42-02	439.4	442.5	1.57	15700	0.27	3	640	128	31	1275	3	16	0.5	23.5	124	0.01
KL42-02	442.5	444.6	1.73	17300	0.35	3.3	670	207	44	695	4	17	0.7	18.0	65	0.01
KL42-02	444.6	446.5	1.03	10300	0.31	3.2	840	214	45	495	4	14	0.7	23.0	39	0.01
KL42-02	446.5	449.5	1.42	14200	0.57	15.8	850	570	33	227	21	12	0.8	15.0	73	0.01
KL42-02	449.5	452.5	1.65	16500	1.08	22.5	850	289	16	618	8	11	0.7	14.5	130	0.01
KL42-02	452.5	455.5	0.93	9300	0.57	8.5	610	274	27	424	11	8	1	10.8	48	0.01
KL42-02	455.5	456.9	0.59	5900	0.29	3	670	144	43	193	9	6	1	11.3	42	0.01
KL42-02	456.9	458.9	0.83	8300	0.16	5.1	183	58	19	376	11	12	0.8	8.5	43	0.01
KL42-02	458.9	461.5	1.8	18000	0.56	13.9	1350	1120	28	791	10	14	1.1	13.0	68	0.01
KL42-02	461.5	464.5	3.35	33500	1.2	30	2700	1910	21	121	8	50	2	31.0	80	0.01
KL42-02	464.5	467.5	4.52	45200	1.95	21.3	3100	1520	22	70	16	87	2.2	20.0	73	0.01
KL42-02	467.5	470.5	5.23	52300	3.89	11.2	2200	900	16	34	1	112	0.7	14.0	86	0.01
KL42-02	470.5	473.5	2.87	28700	4.11	8.1	1540	1280	17	105	5	58	1	20.0	101	0.01
KL42-02	473.5	475.9	1.93	19300	2.88	8	3200	1030	24	28	7	43	0.6	22.5	76	0.01
KL42-02	475.9	479	3.05	30500	3.32	15.7	2800	1560	25	97	8	49	2	29.0	84	0.01
KL42-02	479	482.1	2.09	20900	2.84	9.3	4400	1620	34	241	5	54	3.1	20.0	95	0.01
KL42-02	482.1	485.2	1.26	12600	2.08	5.2	620	239	35	50	2	18	1.7	12.5	73	0.01
KL42-02	485.2	488.3	1.67	16700	1.72	4.4	650	273	63	56	2	26	3.6	26.0	61	0.01
KL42-02	488.3	491.3	1.82	18200	1.74	2.9	6800	3300	50	66	4	39	3.6	17.0	57	0.01
KL42-02	491.3	494.3	1.54	15400	1.84	3.7	2700	620	33	39	3	40	0.8	17.5	50	0.01
KL42-02	494.3	496.6	1.56	15600	1.32	4.8	680	71	25	16	3	48	0.2	28.0	41	0.01
KL42-02	496.6	498.8	2.04	20400	2.8	9.7	3200	1830	26	13	7	48	1.6	33.0	51	0.01
KL42-02	498.8	500.5	0.105	1050	0.2	0.5	450	319	19	3	2	2	0.4	4.0	23	0.01
KL42-02	500.5	502.8	0.055	550	0.7	1.7	3010	3270	4	0.01	0.01	3	0.8	1.9	24	0.01
KL42-02	502.8	504.6	2.79	27900	2.02	9.5	2300	670	72	10	1	168	9	18.0	23	0.01
KL42-02	504.6	506.5	0.098	980	0.19	1.7	1550	3200	24	6	1	3	1.8	2.3	21	0.01
KL42-02	506.5	509.1	0.118	1180	0.14	1.3	1250	1490	35	4	1	2	2.2	3.0	23	0.01
KL42-02	509.1	512	0.0279	279	0.09	0.01	970	287	39	2	0.01	0.01	1.8	2.1	24	0.01
KL42-02	512	514.5	0.04	400	0.08	3.1	2230	3640	15	2	0.01	0.01	4.9	2.2	22	0.01
KL42-02	514.5	516	0.0194	194	0.05	0.01	299	180	19	4	0.01	0.01	0.9	1.2	29	0.01
KL42-02	516	517.9	0.042	420	0.04	0.01	405	68	11	3	0.01	0.01	0.8	1.3	22	0.01
KL42-02	517.9	520.7	0.0141	141	0.04	0.6	730	510	18	6	0.01	0.01	1	1.1	26	0.01
KL42-02	520.7	523.2	0.0288	288	0.06	0.01	421	140	17	6	0.01	0.01	0.8	1.7	29	0.01
KL42-02	523.2	525	0.0091	91	0.02	0.01	173	68	14	3	0.01	0.01	0.2	0.9	22	0.01
KL42-02	525	527.9	0.0369	369	0.03	0.01	113	57	13	5	0.01	0.01	0.2	1.0	15	0.01
KL42-02	527.9	530.5	0.0064	64	0.01	0.01	79	26	9	4	0.01	0.01	0.2	0.5	12	0.01
KL42-02	530.5	533.5	0.0158	158	0.03	0.01	83	28	14	5	0.01	0.01	0.5	0.9	12	0.01
KL42-02	533.5	536.1	0.0195	195	0.03	0.01	224	107	13	3	0.01	0.01	0.7	1.1	14	0.01
KL42-02	536.1	539.4	0.0181	181	0.14	6.2	9600	11400	39	6	0.01	0.01	7.2	6.2	26	0.01
KL42-02	539.4	540.9	0.0064	64	0.05	0.01	368	147	11	2	0.01	0.01	0.2	0.7	16	0.01
KL42-02	540.9	543.9	0.068	680	0.08	0.01	116	28	2	4	0.01	4	0.01	1.1	16	0.01
KL42-02	543.9	545.5	0.399	3990	0.28	2	164	33	55	17	18	12	1.4	2.8	12	0.01
KL42-02	545.5	548.5	0.0108	108	0.01	0.01	15	8	1	0.01	0.01	5	0.01	0.0	104	0.01
KL42-02	548.5	551.5	0.0376	376	0.09	0.01	72	34	32	9	8	2	1.2	0.0	27	0.01
KL42-02	551.5	554.5	0.064	640	0.05	0.01	115	55	32	6	7	4	0.8	1.3	19	0.01
KL42-02	554.5	557.5	0.074	740	0.11	0.5	490	137	38	4	4	6	1	1.8	16	0.01
KL42-02	557.5	560.5	0.22	2200	0.29	1.2	272	41	37	4	6	7	0.6	1.5	20	0.01
KL42-02	560.5	563.5	0.64	6400	0.6	4.5	133	60	58	3	2	18	1.2	3.0	73	0.01
KL42-02	563.5	566.5	0.143	1430	0.08	0.8	156	26	3	6	0.01	5	0.01	2.0	16	0.01
KL42-02	566.5	569.5	0.019	190	0.01	0.01	54	14	3	4	0.01	0.01	0.01	0.5	13	0.01
KL42-02	569.5	571.2	0.0284	284	0.03	0.01	102	33	7	6	0.01	0.01	0.01	0.9	19	0.01
KL42-02	571.2	573.5	0.94	9400	0.64	3.9	195	84	38	398	1	20	0.3	6.0	32	0.01
KL42-02	573.5	575.5	1.43	14300	0.89	5.8	550	146	68	25	3	93	0.9	16.8	44	0.01
KL42-02	575.5	578.4	1.06	10600	0.77	5.3	1420	194	110	23	2	63	1.8	9.0	56	0.01
KL42-02	578.4	581.4	1.96	19600	0.83	8.3	2400	600	160	45	3	28	4.2	7.3	61	0.01
KL42-02	581.4	584.5	0.068	680	0.08	0.6	205	128	30	7	7	5	1.3	1.5	35	0.01
KL42-02	584.5	587.4	0.0208	208	0.03	0.01	103	40	17	12	5	4	2	3.8	29	0.01
KL42-02	587.4	590.1	0.048	480	0.04	0.01	234	64	34	13	6	3	0.7	0.0	34	0.01
KL42-02	590.1	593.1	0.0076	76	0.03	0.01	75	25	35	10	9	2	2	0.0	25	0.01
KL42-02	593.1	595.9	0.031	310	0.04	0.01	70	26	56	4	36	4	5	0.5	16	0.01
KL42-02	595.9	600.1	0.402	4020	0.52	2.1	249	226	31	65	7	8	2.5	3.0	51	0.01
KL42-02	600.1	602.8	0.0285	285	0.01	0.01	98	30	5	2	0.01	0.01	0.01	1.5	14	0.01
KL42-02	602.8	604.8	0.0043	43	0.01	0.01	228	48	4	0.01	0.01	0.01	0.01	0.8	12	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL42-02	604.8	607.9	0.004		40	0.09	0.01	790	266	63	9	0.01	0.01	1.2	1.5	17	0.01
KL42-02	607.9	609.4	0.0079		79	0.02	0.01	209	291	9	0.01	0.01	0.01	0.4	1.0	14	0.01
KL42-02	609.4	611.9	0.0183		183	0.03	0.01	224	55	17	0.01	0.01	0.01	0.3	0.7	13	0.01
KL42-02	611.9	614.7	0.0024		24	0.01	0.01	440	107	5	0.01	0.01	0.01	0.01	0.8	10	0.01
KL42-02	614.7	617.2	0.0109		109	0.01	0.01	790	94	3	0.01	0.01	0.01	0.01	1.0	9	0.01
KL42-02	617.2	620.3	0.0061		61	0.01	0.01	860	99	4	0.01	0.01	0.01	0.01	0.8	10	0.01
KL42-02	620.3	623.3	0.062		620	0.31	0.01	319	65	9	155	2	2	0.01	1.3	10	0.01
KL42-02	623.3	625.3	0.008		80	0.01	0.01	67	23	3	9	0.01	0.01	0.01	0.0	9	0.01
KL42-02	625.3	628.3	0.0137		137	0.02	0.01	51	42	4	7	0.01	0.01	0.01	0.5	9	0.01
KL42-02	628.3	631.4	0.051		510	0.04	0.01	179	45	5	4	0.01	0.01	0.01	1.5	10	0.01
KL42-02	631.4	633.6	0.0089		89	0.02	0.01	205	83	3	4	0.01	0.01	0.01	1.3	8	0.01
KL42-02	633.6	635.5	0.0189		189	0.02	0.01	229	98	5	8	0.01	0.01	0.3	1.3	9	0.01
KL42-02	635.5	638.5	0.0114		114	0.03	0.01	263	103	2	4	0.01	0.01	0.3	0.8	8	0.01
KL42-02	638.5	641.5	0.0192		192	0.04	0.01	790	183	12	11	0.01	0.01	0.6	0.8	8	0.01
KL42-02	641.5	644.5	0.056		560	0.18	1.4	20900	3700	31	14	0.01	0.01	1.5	7.4	20	0.01
KL42-02	644.5	647.1	0.053		530	0.13	0.8	15800	2100	11	0.01	1	0.01	0.01	10.0	17	0.01
KL42-02	647.1	650.1	1.22		12200	1.16	8.5	7300	850	61	29	5	14	0.3	13.4	34	0.01
KL42-02	650.1	653.1	0.51		5100	0.49	5.6	28600	6600	67	5	1	4	2.4	13.9	32	0.01
KL42-02	653.1	655.5	0.044		440	0.26	0.01	20800	4800	22	0.01	2	0.01	0.7	5.9	15	0.01
KL42-02	655.5	656.9	0.044		440	0.26	0.01	20800	4800	22	0.01	2	0.01	0.7	5.9	15	0.01
KL42-02	656.9	659.8	0.0201		201	0.07	0.01	790	239	17	0.01	0.01	0.01	0.01	0.6	16	0.01
KL42-02	659.8	662.1	0.0217		217	0.31	0.01	399	92	8	10	128	0.01	0.3	2.5	14	0.01
KL42-02	662.1	665	0.075		750	0.11	0.7	480	183	14	0.01	1	0.01	0.5	1.8	25	0.01
KL42-02	665	668	0.3		3000	0.3	2	4900	2500	96	3	6	2	2	5.8	20	0.01
KL42-02	668	670.3	0.0097		97	0.02	0.01	2080	378	16	0.01	0.01	0.01	0.01	1.4	14	0.01
KL42-02	670.3	673.1	0.0069		69	0.01	0.01	250	48	11	0.01	0.01	0.01	0.01	0.0	14	0.01
KL42-02	673.1	674.5	0.006		60	0.01	0.01	245	32	7	2	0.01	0.01	0.01	0.0	14	0.01
KL42-02	674.5	677.5	0.067		670	0.03	0.01	193	17	8	0.01	1	0.01	0.01	2.5	17	0.01
KL42-02	677.5	680.3	0.148		1480	0.1	0.6	376	99	14	3	1	0.01	0.01	3.0	16	0.01
KL42-02	680.3	682.3	0.495		4950	0.7	3	1280	309	21	4	1	4	0.01	3.9	19	0.01
KL42-02	682.3	685.4	0.06		600	0.09	0.01	172	47	8	3	1	0.01	0.01	1.5	12	0.01
KL42-02	685.4	686.5	0.0399		399	0.03	0.01	138	14	9	0.01	1	0.01	0.01	1.5	18	0.01
KL42-02	686.5	689.5	0.12		1200	0.15	0.01	357	56	18	4	1	13	0.01	3.8	17	0.01
KL42-02	689.5	692.5	0.68		6800	0.71	3.8	340	15	23	16	1	15	0.01	12.5	32	0.01
KL42-02	692.5	695.5	0.63		6300	0.23	2.7	195	10	8	3	5	15	0.8	2.8	25	0.01
KL42-02	695.5	698.3	0.122		1220	0.09	0.01	190	14	6	12	0.01	2	0.01	1.5	16	0.01
KL42-02	698.3	701.5	0.0217		217	0.01	0.01	118	16	5	3	0.01	0.01	0.01	0.7	24	0.01
KL42-02	701.5	704.5	0.0185		185	0.01	0.01	106	9	4	2	0.01	0.01	0.01	2.0	22	0.01
KL42-02	704.5	706.9	0.101		1010	0.07	0.8	235	30	12	3	2	0.01	0.01	1.5	18	0.01
KL42-02	706.9	709.3	0.0241		241	0.03	0.01	93	9	4	0.01	0.01	0.01	0.01	0.0	18	0.01
KL42-02	709.3	711.3	0.0292		292	0.03	0.01	156	13	9	0.01	0.01	0.01	0.2	0.0	18	0.01
KL42-02	711.3	713.8	0.08		800	0.04	0.6	110	11	8	3	0.01	0.01	0.2	0.8	19	0.01
KL42-02	713.8	716.5	0.0149		149	0.01	0.01	104	12	13	2	0.01	0.01	0.01	0.0	18	0.01
KL42-02	716.5	719.5	0.096		960	0.09	0.8	294	40	9	3	2	0.01	0.2	1.5	20	0.01
KL42-02	719.5	722.5	0.0396		396	0.03	0.01	144	16	10	0.01	0.01	0.01	0.01	1.0	17	0.01
KL42-02	722.5	725.4	0.108		1080	0.14	0.01	118	11	12	2	0.01	0.01	0.4	0.8	18	0.01
KL42-02	725.4	728.5	0.465		4650	0.42	1.7	157	18	8	28	1	9	0.4	5.8	25	0.01
KL42-02	728.5	731.5	0.3		3000	0.23	1.1	124	13	6	143	1	14	0.4	8.8	32	0.01
KL42-02	731.5	734	0.58		5800	0.42	1.7	160	21	13	33	1	16	0.3	7.8	25	0.01
KL42-02	734	737.1	0.28		2800	0.23	2.7	530	93	270	18	3	8	1.2	3.3	22	0.32
KL42-02	737.1	740.2	0.41		4100	0.74	3.4	600	116	780	53	3	6	1.6	6.9	32	0.97
KL42-02	740.2	743.1	0.178		1780	0.11	1.3	460	213	30	30	2	4	0.5	2.5	20	0.01
KL42-02	743.1	744.2	0.69		6900	0.65	3.9	224	14	12	4	5	21	1.2	6.8	38	0.01
KL42-02	744.2	746.5	1.14		11400	0.72	5.3	180	80	150	213	12	16	41	10.5	34	0.01
KL42-02	746.5	749.5	0.92		9200	0.64	3.8	192	40	63	130	14	25	12.8	6.9	32	0.27
KL42-02	749.5	752.5	0.207		2070	0.21	0.9	134	11	10	38	1	31	0.8	1.8	40	0.01
KL42-02	752.5	755.5	0.493		4930	0.17	1.3	261	21	38	0.01	2	0.01	0.2	10.4	36	0.01
KL42-02	755.5	758.5	0.76		7600	0.69	4.5	114	14	6	4	7	28	0.6	4.0	27	0.01
KL42-02	758.5	761.4	0.74		7400	0.06	3.5	148	6	12	3	5	30	0.5	2.0	56	0.01
KL42-02	761.4	764.5	0.478		4780	0.31	1.6	128	24	13	38	1	36	0.7	4.8	36	0.01
KL42-02	764.5	767.5	0.354		3540	0.33	0.8	78	12	7	43	1	16	0.4	5.3	20	0.01
KL42-02	767.5	770.5	0.472		4720	0.34	1	90	13	8	30	1	16	0.3	8.0	21	0.01
KL42-02	770.5	772.8	1.34		13400	0.52	5.1	178	434	86	320	15	28	37	11.5	27	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL42-02	772.8	774.9	1.36	13600	0.87	2.7	132	29	11	10	2	15	1	12.5	15	0.01
KL42-02	774.9	776.8	1.71	17100	0.11	22.2	900	1110	830	20	26	7	42	14.0	44	0.01
KL42-02	776.8	779	0.55	5500	0.06	1.6	154	46	4	15	0.01	8	0.01	3.5	26	0.01
KL42-02	779	781.3	0.409	4090	0.05	1.6	143	41	3	25	1	5	0.01	1.8	15	0.01
KL42-02	781.3	783.2	0.507	5070	0.05	2.8	392	720	85	640	1	6	1.6	5.8	27	0.01
KL42-02	783.2	785.5	0.24	2400	0.04	3.8	870	650	14	6	10	5	0.4	5.0	46	0.01
KL42-02	785.5	788.5	0.2	2000	0.03	1.2	550	276	24	173	2	8	0.8	4.5	40	0.01
KL42-02	788.5	790.6	0.21	2100	0.03	0.8	121	71	12	63	2	9	0.2	3.8	38	0.01
KL42-02	790.6	792	0.318	3180	0.03	1.5	83	31	11	173	2	7	0.5	7.3	50	0.01
KL42-02	792	793.6	0.23	2300	0.02	1.1	84	48	13	48	1	6	1.5	1.8	20	0.01
KL42-02	793.6	796.7	0.25	2500	0.05	1.2	63	28	4	68	0.01	5	0.01	3.0	17	0.01
KL42-02	796.7	799.8	0.344	3440	0.24	1.8	244	197	11	283	1	9	1.4	10.8	53	0.01
KL42-02	799.8	802.9	1.4	14000	0.49	1.7	218	107	17	23	0.01	15	0.01	18.8	61	0.01
KL42-02	802.9	806	0.395	3950	0.2	1	107	29	3	78	0.01	10	0.01	4.5	25	0.01
KL42-02	806	809.1	0.85	8500	0.32	1.4	86	16	18	46	1	12	0.01	8.8	45	0.01
KL42-02	809.1	811.4	0.72	7200	0.25	2.7	1700	326	45	103	3	15	0.01	8.5	41	0.01
KL42-02	811.4	813.4	0.69	6900	0.05	4.7	890	610	370	125	3	5	0.7	8.9	155	0.13
KL42-02	813.4	815.3	0.96	9600	0.43	3.1	1210	630	67	60	2	16	0.01	8.4	57	0.01
KL42-02	815.3	818.4	0.469	4690	0.2	1.6	920	950	38	148	1	14	0.9	12.5	28	0.01
KL42-02	818.4	821.5	0.44	4400	0.25	1.1	119	11	2	8	0.01	16	0.01	3.3	34	0.01
KL42-02	821.5	824.4	1.61	16100	0.87	2.4	243	14	1	12	0.01	27	0.01	10.3	40	0.01
KL42-02	824.4	827.4	1.94	19400	1.08	3.6	220	13	3	24	1	26	0.01	14.0	49	0.01
KL42-02	827.4	830.5	0.83	8300	0.48	1.8	305	19	34	14	1	28	0.01	10.2	49	0.01
KL42-03	0	3.8	0.0052	52	0.01	0.01	76	95	16	2	0.01	0.01	2.4	0.9	16	0.01
KL42-03	3.8	6.7	0.005	50	0.01	0.6	113	49	8	7	0.01	2	1.8	0.8	18	0.01
KL42-03	6.7	9.1	0.0017	17	0.02	0.9	1160	490	8	4	0.01	0.01	2	1.1	16	0.01
KL42-03	9.1	11.9	0.0016	16	0.01	0.5	114	57	5	3	0.01	0.01	1.6	0.0	23	0.01
KL42-03	11.9	14.6	0.0031	31	0.01	0.01	104	45	13	5	0.01	0.01	1.1	0.9	15	0.01
KL42-03	14.6	17.9	0.0011	11	0.09	0.01	152	40	15	5	0.01	2	2.6	1.6	22	0.14
KL42-03	17.9	20.3	0.0021	21	0.21	0.7	167	42	17	7	0.01	0.01	6.1	1.7	18	0.21
KL42-03	20.3	23.9	0.0069	69	0.07	0.01	211	43	13	9	0.01	0.01	5.5	0.7	30	0.13
KL42-03	23.9	26.9	0.0007	7	0.02	1.3	89	40	12	3	0.01	0.01	1.9	1.2	29	0.1
KL42-03	26.9	29.9	0.0008	8	0.01	0.7	45	15	4	4	0.01	0.01	0.7	0.6	32	0.13
KL42-03	29.9	32.5	0.0006	6	0.1	1.4	168	42	8	2	0.01	0.01	2.7	0.8	28	0.47
KL42-03	32.5	35.9	0.0023	23	0.02	0.5	76	35	8	2	0.01	4	1.3	0.5	46	0.1
KL42-03	35.9	38.8	0.0008	8	0.06	0.9	136	56	6	0.01	0.01	0.01	1.6	0.5	38	0.01
KL42-03	38.8	41.4	0.001	10	0.06	0.5	180	32	10	3	0.01	0.01	4.2	1.4	41	0.1
KL42-03	41.4	44.9	0.0006	6	0.02	0.01	54	28	10	3	0.01	2	1.9	0.7	36	0.01
KL42-03	44.9	47.9	0.0012	12	0.01	0.8	40	101	9	2	0.01	0.01	0.9	0.9	18	0.01
KL42-03	47.9	50.9	0.0015	15	0.01	0.7	44	56	7	3	0.01	0.01	1	1.6	21	0.01
KL42-03	50.9	53.9	0.0011	11	0.01	1.2	94	108	16	2	0.01	0.01	2.7	1.6	26	0.01
KL42-03	53.9	56.9	0.1975	1975	0.08	56	30400	19600	690	14	0.01	3	75	54.5	32	5.64
KL42-03	56.9	59.9	0.0018	18	0.01	1.2	215	143	11	3	0.01	0.01	1.8	1.5	16	0.01
KL42-03	59.9	62.4	0.001	10	0.01	0.01	53	47	8	3	0.01	4	0.4	0.6	22	0.01
KL42-03	62.4	65.5	0.0006	6	0.01	0.01	27	21	6	3	0.01	0.01	0.3	0.8	23	0.01
KL42-03	65.5	68.9	0.0037	37	0.01	0.7	540	275	12	8	0.01	0.01	3.4	2.1	21	0.15
KL42-03	68.9	71.4	0.0006	6	0.01	0.01	115	29	5	3	0.01	0.01	2.4	0.9	21	0.01
KL42-03	71.4	74.2	0.0007	7	0.02	0.01	45	33	7	2	0.01	0.01	0.4	1.5	22	0.01
KL42-03	74.2	77.2	0.0008	8	0.04	0.01	30	26	14	4	0.01	0.01	0.7	1.5	32	0.01
KL42-03	77.2	80.2	0.0011	11	0.04	0.01	68	90	7	2	0.01	0.01	1.1	1.6	27	0.01
KL42-03	80.2	83.9	0.0008	8	0.03	0.01	98	42	11	2	0.01	0.01	1.1	1.9	18	0.01
KL42-03	83.9	86.9	0.0041	41	0.05	1.4	950	850	49	5	0.01	0.01	3.4	9.8	31	0.1
KL42-03	86.9	89.9	0.0017	17	0.03	0.01	182	136	18	4	0.01	0.01	11.1	2.9	21	0.12
KL42-03	89.9	92.9	0.0012	12	0.03	0.7	103	49	18	2	0.01	0.01	10.2	1.8	22	0.01
KL42-03	92.9	95.9	0.0027	27	0.03	0.9	169	193	24	4	0.01	0.01	7.7	4.3	29	0.1
KL42-03	95.9	98.8	0.0046	46	0.06	1.6	580	1020	50	2	3	0.01	20.4	13.3	51	0.2
KL42-03	98.8	101.9	0.002	20	0.33	1	1010	300	170	7	1	0.01	14	3.2	51	0.29
KL42-03	101.9	104.9	0.0019	19	0.09	1.1	407	314	51	9	0.01	3	4.1	1.3	91	0.12
KL42-03	104.9	107.4	0.0361	361	0.23	1.9	440	239	170	19	2	6	36	3.7	52	0.15
KL42-03	107.4	110.3	4.29	42900	1.84	28	520	930	14600	108	57	12	1600	21.0	220	3.98
KL42-03	110.3	113.9	0.34	3400	0.73	100	6300	42400	1130	120	52	0.01	73	48.0	158	1.51
KL42-03	113.9	116.7	0.0162	162	0.99	36	7100	17700	180	268	6	3	20	19.5	133	0.5
KL42-03	116.7	122.8	0.013	130	0.67	97	8000	67400	100	95	2	0.01	38	26.0	126	0.85

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL42-03	122.8	125.8	0.0066		66	0.81	13.6	2420	10100	49	50	2	2	18.8	4.5	168	0.3
KL42-03	125.8	128.6	0.0078		78	0.51	6.7	1550	5800	46	58	1	0.01	22.8	4.0	175	0.19
KL42-03	128.6	131.3	0.0051		51	0.21	3.6	2330	3050	77	46	0.01	0.01	8.8	3.2	118	0.51
KL42-03	131.3	134	0.0156		156	0.45	2.1	7300	2800	120	148	4	0.01	20	2.8	66	0.4
KL42-03	134	137.9	0.0048		48	0.28	0.9	4990	1410	68	640	1	3	8.8	2.5	57	0.15
KL42-03	137.9	140.3	0.252		2520	0.77	4.1	6600	4700	630	1360	4	2	720	12.5	79	0.87
KL42-03	140.3	143.2	0.093		930	2.88	12.3	7300	3000	450	740	34	10	130	32.0	115	0.86
KL42-03	143.2	146.3	0.086		860	0.47	6.4	3970	1150	480	2330	46	6	100	18.8	85	0.42
KL42-03	146.3	149.9	0.083		830	0.88	18.9	6420	3380	270	385	18	0.01	120	19.6	38	0.81
KL42-03	149.9	152.9	0.0328		328	0.26	5	2470	680	60	153	8	3	32	8.5	19	0.22
KL42-03	152.9	155.1	0.0151		151	0.15	2.3	1080	263	38	45	10	0.01	11	4.8	16	0.11
KL42-03	155.1	158.5	0.0158		158	0.11	2.3	990	228	46	71	12	2	9.3	9.0	20	0.01
KL42-03	158.5	161.8	0.0028		28	0.07	0.7	560	144	16	18	2	0.01	1.5	2.0	18	0.1
KL42-03	161.8	164.2	0.0054		54	0.1	1.2	1610	260	32	13	9	0.01	3.1	3.8	23	0.01
KL42-03	164.2	167.1	0.0083		83	0.08	1.2	420	182	27	39	6	0.01	2.9	2.2	20	0.01
KL42-03	167.1	170.4	0.0126		126	0.1	1.9	570	172	45	65	16	0.01	5.8	3.2	20	0.01
KL42-03	170.4	173.8	0.0094		94	0.08	0.9	660	110	31	73	7	0.01	3.3	2.0	18	0.01
KL42-03	173.8	177	0.0141		141	0.06	0.6	1210	78	42	79	12	0.01	3.6	4.2	16	0.01
KL42-03	177	180.3	0.0356		356	0.12	1.2	460	107	110	157	6	2	6.2	3.0	21	0.12
KL42-03	180.3	183.4	0.044		440	0.2	1.6	1240	160	220	216	14	2	8.9	6.0	22	0.11
KL42-03	183.4	188.1	0.098		980	0.22	3.8	4600	440	300	78	28	3	11.1	11.2	19	0.12
KL42-03	188.1	190.7	0.022		220	0.1	2.2	1020	184	28	26	7	0.01	2.6	3.2	16	0.01
KL42-03	190.7	193.9	0.093		930	0.21	3.3	3280	730	290	35	7	0.01	40	8.5	15	0.01
KL42-03	193.9	196.2	0.128		1280	0.28	3.2	3750	1570	360	46	50	3	38	22.5	15	0.12
KL42-03	196.2	198.8	0.59		5900	0.98	10.8	2610	560	220	396	102	4	6.9	13.8	24	0.01
KL42-03	198.8	201.7	0.0274		274	0.12	1.6	1030	217	40	90	22	0.01	4.1	3.0	14	0.01
KL42-03	201.7	204.4	1.34	13400	0.24	1.7	47	20	1	165	0.01	16	0.9	3.5	135	0.01	
KL42-03	204.4	207.2	0.112	1120	0.16	2.3	1090	61	52	160	18	0.01	1.8	5.0	14	0.01	
KL42-03	207.2	210.5	0.0257	257	0.17	4.4	1810	343	49	78	44	0.01	1.7	5.5	9	0.01	
KL42-03	210.5	213.2	0.104	1040	0.4	3.4	9000	163	84	133	32	3	2.4	12.0	13	0.01	
KL42-03	213.2	215.9	0.046	460	0.16	1.8	3320	520	120	44	16	2	2.6	7.5	11	0.01	
KL42-03	215.9	218.9	0.103	1030	0.43	2.5	1980	298	150	321	28	10	2.8	11.6	16	0.01	
KL42-03	218.9	221.8	0.38	3800	0.58	6.1	1980	241	500	530	16	15	10.2	10.5	24	0.12	
KL42-03	221.8	224.9	0.33	3300	0.43	6.1	8700	208	270	500	18	14	4.7	10.0	28	0.01	
KL42-03	224.9	226.9	0.12	1200	0.41	4.5	13400	290	140	128	8	13	4.6	8.8	15	0.01	
KL42-03	226.9	230.9	0.154	1540	0.47	3	5200	288	120	504	7	14	2.5	6.8	21	0.01	
KL42-03	230.9	233.9	0.62	6200	0.95	5.7	7300	110	160	252	5	54	6.5	12.0	21	0.01	
KL42-03	233.9	236.9	0.62	6200	1.19	3.6	3950	110	67	122	1	32	2.5	13.8	26	0.01	
KL42-03	236.9	239.9	1.23	12300	1.8	3.4	3120	39	37	79	1	45	3.1	15.5	29	0.01	
KL42-03	239.9	242.9	0.88	8800	1.28	2	420	38	57	48	4	27	3.4	7.5	26	0.01	
KL42-03	242.9	245.9	0.59	5900	0.67	1.8	1390	54	91	26	1	29	6.4	10.3	25	0.01	
KL42-03	245.9	248.9	0.67	6700	0.63	2.3	388	128	96	71	1	30	4	11.9	51	0.01	
KL42-03	248.9	251.9	1.12	11200	0.92	3.4	364	115	64	56	1	37	5.7	13.5	61	0.01	
KL42-03	251.9	254.9	1.56	15600	0.99	4.5	321	73	110	197	0.01	11	5.1	13.0	51	0.01	
KL42-03	254.9	257.9	1.4	14000	1	4.5	440	92	310	78	0.01	28	12.8	17.0	48	0.16	
KL42-03	257.9	260.9	0.96	9600	0.64	4.7	530	192	660	10	0.01	25	20	9.7	88	0.33	
KL42-03	260.9	263.9	0.501	5010	1	1.7	590	105	440	17	0.01	19	11	13.0	69	0.01	
KL42-03	263.9	266.9	0.95	9500	1.25	3.1	324	56	56	21	1	30	6	20.0	59	0.01	
KL42-03	266.9	269.9	0.65	6500	1.07	2.5	2180	45	38	18	1	29	5.6	16.3	24	0.01	
KL42-03	269.9	272.9	1.23	12300	0.72	2.5	127	56	39	805	0.01	36	3.7	12.5	38	0.01	
KL42-03	272.9	275.9	1.77	17700	1.72	4.1	124	25	49	208	0.01	28	4	28.0	41	0.01	
KL42-03	275.9	278.9	0.431	4310	0.41	1.4	236	60	51	372	0.01	12	5.3	11.0	36	0.01	
KL42-03	278.9	281.9	0.66	6600	0.42	1.2	5130	295	190	1020	0.01	11	6.6	14.0	65	0.94	
KL42-03	281.9	284.9	0.399	3990	1.44	4.1	1810	1620	800	1280	0.01	12	28	7.3	149	6.7	
KL42-03	284.9	287.9	0.161	1610	0.35	2.6	1210	1850	90	550	1	4	9.3	5.6	150	0.8	
KL42-03	287.9	290.9	0.204	2040	0.5	4.5	5330	2680	330	55	0.01	7	14	12.3	146	1.56	
KL42-03	290.9	293.3	0.131	1310	0.36	6.7	4200	12700	330	178	0.01	10	12.2	19.6	162	1.36	
KL42-03	293.3	296.9	0.493	4930	1.5	3.9	990	560	1400	2010	1	8	44	12.3	139	2.76	
KL42-03	296.9	302.9	0.179	1790	2.38	4.7	2010	3980	520	70	3	8	7.3	17.5	117	1.8	
KL42-03	302.9	308	0.405	4050	0.34	0.7	2410	140	130	158	0.01	9	2.6	2.9	56	0.1	
KL42-03	308	312.9	0.35	3500	0.26	0.7	2500	214	190	231	0.01	17	1.1	6.2	37	0.01	
KL42-03	312.9	318	0.34	3400	0.27	1.5	480	140	330	900	0.01	12	1.1	5.9	121	0.01	
KL42-03	318	320.9	0.8	8000	0.39	1.3	186	25	20	187	0.01	32	0.6	6.3	41	0.01	

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL42-03	320.9	326.3	0.26	2600	0.21	0.7	287	175	23	440	0.01	7	1.9	3.5	71	0.01
KL42-03	326.3	329.9	0.56	5600	0.38	1	1670	220	41	87	1	14	1.1	5.8	50	0.01
KL42-03	329.9	332.9	0.94	9400	0.58	1.8	261	106	180	216	2	44	5.6	7.3	51	0.16
KL42-03	332.9	335.1	0.73	7300	0.47	1.6	85	37	24	80	0.01	11	1.1	3.8	39	0.01
KL42-03	335.1	337.9	0.56	5600	0.26	1.5	228	78	37	610	0.01	13	1.7	4.5	42	0.01
KL42-03	337.9	340.4	0.63	6300	0.7	2.9	5640	1140	340	22	5	8	6.8	23.8	86	0.14
KL42-03	340.4	343	1.32	13200	1.22	4.4	3400	1100	1580	6	6	13	5.3	16.5	78	0.22
KL42-03	343	345.6	0.88	8800	0.26	2.8	1630	361	140	138	2	8	2.3	11.3	54	0.01
KL42-03	345.6	347.9	1.18	11800	0.61	2	171	42	130	461	3	20	2.6	20.0	65	0.01
KL42-03	347.9	351.3	0.99	9900	0.3	4.8	560	327	160	79	5	16	2.3	13.5	104	0.01
KL42-03	351.3	353.5	0.296	2960	0.1	1.4	131	36	33	121	2	5	2.7	3.0	24	0.01
KL42-03	353.5	356.5	0.96	9600	0.31	3.1	1060	148	36	605	2	12	2.3	6.5	92	0.01
KL42-03	356.5	359.2	1.67	16700	0.78	3	114	20	36	431	1	16	2	8.0	68	0.01
KL42-03	359.2	362.3	1.68	16800	1.19	3.4	287	34	39	36	2	19	2.5	14.8	40	0.01
KL42-03	362.3	365.4	1.74	17400	0.49	3.1	172	142	67	231	1	11	3.3	4.5	24	0.01
KL42-03	365.4	368.9	1.07	10700	0.77	2	530	350	60	16	0.01	14	2.2	10.3	39	0.01
KL42-03	368.9	371.9	1.54	15400	1.12	2.3	590	71	10	6	0.01	15	1	12.5	27	0.01
KL42-03	371.9	374.9	3.34	33400	1.56	3.9	610	212	40	93	0.01	40	1.8	11.0	26	0.01
KL42-03	374.9	377.9	0.56	5600	1.7	12.2	20500	7200	2600	381	0.01	9	100	13.5	45	0.36
KL42-03	377.9	380.9	0.87	8700	0.98	7.6	2050	610	240	19	8	15	7.3	8.8	36	0.01
KL42-03	380.9	383.9	0.54	5400	0.94	8.2	1810	332	170	7	22	46	3.4	11.5	30	0.01
KL42-03	383.9	386.9	3.08	30800	2.16	11.5	3000	154	29	9	2	49	2.7	17.0	37	0.01
KL42-03	386.9	389.9	4.14	41400	2.54	7	1600	70	3	311	1	48	0.7	17.0	34	0.01
KL42-03	389.9	392.9	2.87	28700	1.24	6.2	1520	81	2	10	1	28	0.6	13.0	17	0.01
KL42-03	392.9	395.9	4.58	45800	3	14.7	1550	540	25	5	5	43	3.9	15.0	36	0.01
KL42-03	395.9	398.9	7.18	71800	5.26	19.3	810	1000	10	0.01	6	54	1.8	18.8	30	0.01
KL42-03	398.9	401.9	2.67	26700	2.1	4.3	770	520	11	2	1	16	1.8	0.0	18	0.01
KL42-03	401.9	404.9	1.94	19400	1.6	3	710	261	24	13	0.01	28	2	5.0	28	0.01
KL42-03	404.9	407.9	0.99	9900	1.21	2.6	960	700	61	28	4	20	4.6	6.8	31	0.01
KL42-03	407.9	410.9	3.98	39800	2.78	6.7	1770	190	18	13	0.01	39	2.4	23.8	26	0.01
KL42-03	410.9	413.9	1.83	18300	1.86	18.2	1960	182	76	36	7	27	4.2	13.5	74	0.01
KL42-03	413.9	416.9	1.66	16600	4.53	7.1	1230	291	53	16	6	28	4	14.5	62	0.01
KL42-03	416.9	419.9	2.17	21700	3.22	7.8	1450	196	20	21	4	17	12	14.0	50	0.01
KL42-03	419.9	422.9	1.89	18900	3.86	4.2	1230	134	13	10	4	17	2.6	13.5	40	0.01
KL42-03	422.9	425.9	2.77	27700	8.15	8.4	2020	500	21	8	8	18	6.2	19.5	44	0.01
KL42-03	425.9	428.9	1.85	18500	2.83	10.2	5900	64	61	3	27	40	2.4	14.0	76	0.01
KL42-03	428.9	431.4	2.99	29900	1.51	22.5	147	135	290	6	51	75	44	18.0	91	0.8
KL42-03	431.4	434.3	2.25	22500	0.61	22	2900	1790	1530	121	3	34	1210	13.0	96	2.81
KL42-03	434.3	436.4	1.79	17900	0.49	91	1750	900	1220	226	65	18	2620	15.7	98	4.17
KL42-03	436.4	437.5	2.91	29100	0.9	82	1840	1310	2100	134	35	54	1035	27.0	106	2.9
KL42-03	437.5	440.9	1.17	11700	0.5	90	1280	1260	950	580	62	20	1980	13.0	96	3.67
KL42-03	440.9	443.9	1.13	11300	0.4	6.4	123	193	150	133	50	21	82	13.0	105	0.13
KL42-03	443.9	447	1.17	11700	0.46	31.3	950	840	500	103	8	21	1730	16.0	107	1.52
KL42-03	447	449.9	1.12	11200	0.33	8.3	1000	420	870	270	6	16	480	16.0	141	2.5
KL42-03	449.9	451.8	0.69	6900	0.23	2.3	610	279	58	96	46	10	24	9.0	96	0.01
KL42-03	451.8	454.9	1.28	12800	0.21	2.1	326	173	44	150	6	19	5.2	12.0	93	0.01
KL42-03	454.9	458	1.02	10200	0.17	2.8	200	292	79	99	6	17	4.1	11.0	147	0.01
KL42-03	458	461.3	0.85	8500	0.25	7.7	307	339	210	187	6	15	18	13.0	175	0.01
KL42-03	461.3	464.9	1.19	11900	0.77	71	900	265	230	183	50	14	655	12.5	72	0.38
KL42-03	464.9	467.9	0.86	8600	0.81	4.7	120	154	42	48	38	14	12.3	13.5	85	0.01
KL42-03	467.9	470.9	1.2	12000	0.28	2.7	56	137	46	540	3	13	6.6	13.2	130	0.01
KL42-03	470.9	473.9	0.96	9600	0.49	2.2	52	193	30	14	5	14	4.6	7.5	95	0.01
KL42-03	473.9	476.9	1.42	14200	0.17	6.3	37	108	62	95	2	18	30	17.0	123	0.01
KL42-03	476.9	479.2	1.04	10400	0.26	2	60	250	70	6	2	18	50	17.0	70	0.01
KL42-03	479.2	481.9	1.45	14500	0.16	5.8	367	880	470	26	2	12	210	16.0	87	0.17
KL42-03	481.9	484.9	1.01	10100	0.13	10.2	154	710	170	153	4	9	220	12.5	58	0.15
KL42-03	484.9	488	0.62	6200	0.09	8.6	99	321	100	50	3	7	70	9.5	46	0.23
KL42-03	488	491.1	1.24	12400	0.17	3.7	128	296	39	22	2	12	26	11.5	72	0.16
KL42-03	491.1	494.2	0.458	4580	0.22	1.9	107	135	23	42	6	6	12	8.5	59	0.01
KL42-03	494.2	497	0.83	8300	0.18	2.6	52	141	33	34	3	8	24	10.0	67	0.01
KL42-03	497	500.1	0.68	6800	0.25	5.2	67	119	40	16	3	10	10.6	9.8	60	0.01
KL42-03	500.1	503.2	0.412	4120	0.26	1.7	78	205	25	22	6	11	3.8	7.0	61	0.01
KL42-03	503.2	506.3	0.7	7000	0.3	1.2	137	510	30	174	3	12	6	8.2	75	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL42-03	506.3	509.3	0.33	3300	0.2	1	75	58	5	39	0.01	7	1.2	4.0	70	0.01
KL42-03	509.3	512.9	0.458	4580	0.2	1.6	74	32	3	94	2	8	1.3	5.3	68	0.01
KL42-03	512.9	515.3	0.175	1750	0.09	0.8	36	22	3	39	0.01	6	2.4	2.5	69	0.01
KL42-03	515.3	518.3	0.161	1610	0.11	0.8	33	16	10	34	0.01	10	2.3	7.5	65	0.01
KL42-03	518.3	521.5	0.382	3820	0.28	1.2	184	70	3	18	0.01	7	0.6	3.0	66	0.01
KL42-03	521.5	524.6	0.68	6800	0.29	2	251	180	11	31	0.01	13	2.9	9.3	67	0.01
KL42-03	524.6	527.7	0.31	3100	0.14	1.4	94	61	6	13	0.01	9	0.4	4.5	46	0.01
KL42-03	527.7	530.7	1.47	14700	0.69	4.5	103	19	4	32	0.01	18	0.3	10.8	71	0.01
KL42-03	530.7	533.5	0.76	7600	0.1	1.6	87	62	26	70	2	10	5.6	6.2	145	0.01
KL42-03	533.5	536.4	0.371	3710	0.04	0.01	125	89	24	124	0.01	13	3.5	12.0	158	0.01
KL42-03	536.4	539.5	0.3	3000	0.03	0.8	211	176	18	195	1	10	6.1	7.5	42	0.01
KL42-03	539.5	542.6	0.28	2800	0.02	0.8	113	740	6	117	0.01	6	2.9	5.3	193	0.01
KL42-03	542.6	545.7	0.25	2500	0.02	1.6	70	142	9	121	0.01	9	7	10.2	181	0.01
KL42-03	545.7	548.8	0.31	3100	0.05	2.4	375	440	35	168	0.01	8	7.3	7.5	215	0.01
KL42-03	548.8	551.9	0.26	2600	0.04	1.2	85	167	46	437	2	24	18	16.9	247	0.01
KL42-03	551.9	554.9	0.86	8600	0.29	2.5	172	126	110	327	3	22	18.9	16.0	143	0.01
KL42-03	554.9	557.9	1.04	10400	0.39	2.9	145	75	29	107	0.01	14	10.6	8.0	166	0.01
KL42-03	557.9	560.9	0.71	7100	0.11	4.2	58	86	20	106	0.01	10	26	6.8	187	0.01
KL42-03	560.9	563.9	0.6	6000	0.12	3.3	113	137	21	58	0.01	13	12.8	7.2	169	0.01
KL42-03	563.9	566.9	0.41	4100	0.05	2.5	255	200	32	121	0.01	14	5.2	6.3	222	0.01
KL42-03	566.9	569.9	0.358	3580	0.02	1.4	236	180	47	86	0.01	14	7	7.2	219	0.01
KL42-03	569.9	572.9	0.22	2200	0.01	1.1	178	119	11	43	0.01	6	2.5	3.0	174	0.01
KL42-03	572.9	575.9	0.31	3100	0.02	2.4	204	110	260	37	2	4	36	2.3	199	0.01
KL42-03	575.9	578.9	0.62	6200	0.07	3.5	224	100	350	243	3	19	28	9.1	193	0.01
KL42-03	578.9	581.9	0.501	5010	0.11	1.4	158	102	65	36	0.01	6	9.8	3.0	175	0.01
KL42-03	581.9	584.9	0.66	6600	0.18	3.4	159	59	150	40	1	13	46	3.8	163	0.01
KL42-03	584.9	587.9	0.52	5200	0.16	1.2	62	42	30	39	1	11	6.5	3.9	96	0.01
KL42-03	587.9	590.9	0.451	4510	0.04	3.5	105	140	100	198	1	8	68	4.4	113	0.1
KL42-03	590.9	593.9	0.54	5400	0.07	2.4	132	132	110	102	3	7	54	5.0	141	0.01
KL42-03	593.9	596.9	0.327	3270	0.08	7	132	306	80	136	2	7	79	5.5	171	0.18
KL42-03	596.9	599.9	0.3	3000	0.02	3.2	48	161	65	117	1	8	37	4.5	218	0.01
KL42-03	599.9	602.9	0.467	4670	0.04	2.1	81	126	62	89	1	6	10.8	3.8	159	0.01
KL42-03	602.9	605.9	0.406	4060	0.08	2.3	31	90	23	156	1	7	8	3.5	148	0.01
KL42-03	605.9	608.9	0.55	5500	0.08	3.2	95	235	59	190	0.01	7	32	4.5	252	0.01
KL42-03	608.9	611.9	0.56	5600	0.06	3.5	96	168	53	35	1	9	33	4.0	185	0.01
KL42-03	611.9	614.9	0.438	4380	6.02	3.6	139	292	41	15	2	7	58	4.5	129	0.01
KL42-03	614.9	617.9	1.21	12100	0.37	2.7	61	87	28	16	1	27	11	12.2	131	0.01
KL42-03	617.9	620.9	0.79	7900	0.1	1.7	193	140	92	53	1	12	74	4.8	186	0.32
KL42-03	620.9	623.9	0.32	3200	0.05	1	81	92	67	73	1	10	1.9	7.8	208	0.28
KL42-03	623.9	626.9	0.507	5070	0.1	1.5	126	88	45	58	0.01	8	16	4.1	187	0.15
KL42-03	626.9	629.9	0.441	4410	0.09	1	219	121	31	61	0.01	7	1.6	5.5	257	0.01
KL42-03	629.9	632.9	0.33	3300	0.06	1	108	50	10	83	1	6	2.3	3.3	211	0.01
KL42-03	632.9	635.9	0.183	1830	0.04	1	328	102	140	85	1	4	7.8	3.3	238	0.19
KL42-03	635.9	638.9	0.132	1320	0.02	1.1	173	72	110	132	1	5	4.3	2.7	135	0.16
KL42-03	638.9	641.9	0.164	1640	0.01	0.8	182	76	91	102	1	4	7.9	2.5	148	0.24
KL42-03	641.9	644.9	0.22	2200	0.01	1.2	263	87	110	48	1	6	12.3	3.0	180	0.28
KL42-03	644.9	647.9	0.165	1650	0.01	0.9	176	88	67	53	1	4	35	3.3	215	0.11
KL42-03	647.9	650.9	0.179	1790	0.01	1.3	192	108	110	39	0.01	6	38	1.3	168	0.27
KL42-03	650.9	653.9	0.2	2000	0.02	0.9	122	36	57	169	0.01	5	8.3	4.0	201	0.14
KL42-03	653.9	656.9	0.184	1840	0.02	0.9	106	38	60	165	0.01	6	2.9	2.0	108	0.17
KL42-03	656.9	659.9	0.51	5100	0.02	1.6	221	118	160	97	0.01	10	9	3.3	207	0.23
KL42-03	659.9	662.9	0.401	4010	0.01	1.4	225	79	78	152	1	7	7.4	3.5	155	0.2
KL42-03	662.9	665.9	0.37	3700	0.05	1.6	124	53	22	62	1	7	4.1	3.8	187	0.01
KL42-03	665.9	668.9	0.34	3400	0.09	8.3	630	248	160	84	1	8	56	6.8	114	0.32
KL42-03	668.9	671.9	0.28	2800	0.09	1.9	362	113	37	76	1	6	3.5	2.3	140	0.11
KL42-03	671.9	674.9	0.26	2600	0.07	1.6	186	76	50	71	2	5	7	5.3	81	0.14
KL42-03	674.9	677.9	0.19	1900	0.06	5.5	161	75	35	90	1	6	12.6	3.0	128	0.01
KL42-03	677.9	680.9	0.191	1910	0.03	7.6	169	206	60	221	1	5	24	2.8	175	0.01
KL42-03	680.9	683.9	0.27	2700	0.04	4.9	162	162	75	173	1	6	10.8	4.5	164	0.1
KL42-03	683.9	686.9	0.33	3300	0.18	13.7	239	165	34	1070	3	9	6.9	6.3	149	0.01
KL42-03	686.9	689.9	0.26	2600	0.03	2.6	120	65	14	82	1	9	1	3.9	228	0.01
KL42-03	689.9	692.9	0.308	3080	0.05	4.1	2280	860	30	117	2	15	3.7	7.5	175	0.1
KL42-03	692.9	695.9	0.61	6100	0.12	5.6	680	290	31	446	3	8	4.4	7.6	221	0.14

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL42-03	695.9	698.9	0.62	6200	0.15	8.9	3340	1540	58	196	1	8	7	3.5	195	0.26
KL42-03	698.9	701.9	0.53	5300	0.11	7.1	290	169	73	184	1	9	11	4.7	187	0.1
KL42-03	701.9	704.9	0.25	2500	0.09	2.1	173	75	30	110	2	7	3.5	2.8	167	0.01
KL42-03	704.9	707.9	0.24	2400	0.18	2.3	151	85	14	96	1	7	0.5	3.3	126	0.01
KL42-03	707.9	710.9	0.32	3200	0.08	1.7	373	191	28	237	1	6	3.5	3.8	156	0.01
KL42-03	710.9	713.9	0.33	3300	0.04	2.2	325	152	31	840	1	10	6.4	4.0	164	0.01
KL42-03	713.9	716.9	0.62	6200	0.17	13.2	1280	2680	94	163	4	9	14.5	3.0	137	0.3
KL42-03	716.9	719.9	0.55	5500	0.13	13.8	590	209	140	213	2	8	30	5.3	134	0.21
KL42-03	719.9	722.9	0.491	4910	0.13	4.8	1120	319	190	240	2	9	4	5.5	155	0.41
KL42-03	722.9	725.9	1	10000	0.35	47	3100	1550	75	207	9	6	34	11.0	148	0.46
KL42-03	725.9	728.9	0.27	2700	0.1	3.9	281	211	74	110	1	10	1.9	4.0	160	0.01
KL42-03	728.9	731.9	0.444	4440	0.22	10.9	333	390	84	156	3	10	8.8	4.8	151	0.1
KL42-03	731.9	734.9	0.411	4110	0.19	13.1	238	251	42	166	7	5	10.2	4.0	160	0.01
KL42-03	734.9	737.9	0.27	2700	0.11	7.4	500	285	28	147	4	4	5.8	5.3	211	0.01
KL42-03	737.9	740.9	0.374	3740	0.11	6.8	388	384	20	150	2	5	5.3	4.3	164	0.01
KL42-03	740.9	743.9	0.322	3220	0.12	9.6	2860	1250	32	110	5	4	5.6	3.0	200	0.14
KL42-03	743.9	746.9	0.29	2900	0.13	5.1	378	400	13	66	4	3	2.8	3.5	174	0.01
KL42-03	746.9	749.9	0.178	1780	0.1	5.2	110	211	11	81	3	6	1.5	2.0	117	0.01
KL42-03	749.9	752.9	0.28	2800	0.08	5.2	118	94	13	149	3	5	2.4	2.8	124	0.01
KL42-03	752.9	755.9	0.29	2900	0.09	9.8	81	106	28	123	3	4	4.4	4.3	124	0.01
KL42-03	755.9	758.9	0.436	4360	0.15	14.3	210	144	81	75	3	8	6.3	5.8	135	0.01
KL42-03	758.9	761.9	0.23	2300	0.11	7.4	143	142	31	67	1	9	4.6	5.3	132	0.01
KL42-03	761.9	764.9	0.157	1570	0.09	3.1	164	167	20	75	1	7	5.7	3.5	142	0.01
KL42-03	764.9	767.9	0.22	2200	0.06	2.5	183	234	20	109	1	14	4.7	8.6	151	0.01
KL42-03	767.9	770.9	0.275	2750	0.09	4.8	170	266	82	92	1	10	13.1	5.3	136	0.01
KL42-03	770.9	773.9	0.27	2700	0.07	5.9	208	170	68	119	1	8	7.8	3.9	214	0.01
KL42-03	773.9	776.9	0.72	7200	0.21	8.7	286	232	43	79	0.01	25	4.6	8.3	104	0.01
KL42-03	776.9	779.9	0.34	3400	0.15	3.3	287	113	12	67	0.01	17	0.9	6.8	99	0.01
KL42-03	779.9	782.9	0.22	2200	0.14	2.4	75	38	9	49	0.01	13	0.3	3.5	103	0.01
KL42-03	782.9	785.9	0.24	2400	0.14	3.5	106	91	15	29	0.01	16	1.2	5.8	84	0.01
KL42-03	785.9	788.9	0.466	4660	0.24	5	171	157	20	96	0.01	17	1.1	7.3	94	0.01
KL42-03	788.9	791.9	0.452	4520	0.21	4.5	81	105	5	213	0.01	13	0.9	5.8	85	0.01
KL42-03	791.9	794.9	0.3	3000	0.16	3.3	94	150	13	97	1	14	0.8	5.5	79	0.01
KL42-03	794.9	797.9	0.487	4870	0.27	5.6	109	264	35	126	1	17	1.1	8.8	106	0.01
KL42-03	797.9	800.9	0.22	2200	0.13	1.6	85	39	10	94	0.01	15	0.01	4.0	103	0.01
KL42-03	800.9	803.9	0.25	2500	0.13	1.4	80	30	11	110	0.01	13	0.01	2.5	112	0.01
KL42-03	803.9	806.9	0.25	2500	0.14	1.3	148	47	21	146	0.01	11	0.7	2.8	92	0.01
KL42-03	806.9	809.9	0.32	3200	0.15	2.4	185	51	12	152	0.01	19	0.5	5.8	80	0.01
KL42-03	809.9	812.9	0.362	3620	0.11	5.4	1230	570	45	153	1	13	5.5	9.5	92	0.12
KL42-03	812.9	815.9	0.29	2900	0.11	1.3	84	36	18	410	1	17	1.4	5.3	71	0.01
KL42-03	815.9	818.9	1.04	10400	0.28	3.8	148	22	14	112	2	275	0.4	13.0	46	0.01
KL42-03	818.9	821.6	1.76	17600	0.68	4.2	158	10	1	136	1	87	0.01	7.0	26	0.01
KL42-03	821.6	823.3	0.56	5600	0.16	2	111	13	1	22	0.01	32	0.01	2.5	59	0.01
KL42-03	823.3	826.4	0.365	3650	0.23	1.1	72	9	3	146	0.01	14	0.01	2.3	29	0.01
KL42-03	826.4	829.5	0.06	600	0.01	0.01	52	15	2	18	0.01	11	0.01	1.3	36	0.01
KL42-03	829.5	832.6	0.26	2600	0.13	1	73	17	5	15	0.01	15	0.01	3.0	32	0.01
KL42-03	832.6	835.7	0.11	1100	0.07	1.1	119	68	4	16	2	18	0.01	3.8	39	0.01
KL42-03	835.7	838.8	0.162	1620	0.17	0.6	82	9	1	9	0.01	32	0.01	2.0	48	0.01
KL42-03	838.8	841.9	0.23	2300	0.11	0.8	63	10	3	8	0.01	24	0.2	5.3	36	0.01
KL42-03	841.9	845	0.153	1530	0.08	0.9	54	13	5	55	0.01	27	0.01	8.7	44	0.01
KL42-03	845	848	0.24	2400	0.09	1	40	7	0.01	49	0.01	4	0.01	1.9	21	0.01
KL42-03	848	850.3	0.076	760	0.05	0.6	27	6	0.01	10	0.01	6	0.4	0.8	13	0.01
KL42-03	850.3	853.7	0.442	4420	0.49	1.4	86	10	2	21	0.01	27	0.01	7.0	36	0.01
KL42-03	853.7	856.2	0.67	6700	0.69	2.1	314	16	0.01	8	0.01	28	0.2	7.0	51	0.01
KL42-03	856.2	859.3	0.57	5700	0.55	1.5	166	10	0.01	7	0.01	29	0.01	4.8	44	0.01
KL42-03	859.3	862.4	0.64	6400	0.46	1.6	135	9	0.01	16	0.01	15	0.01	4.8	38	0.15
KL42-03	862.4	866	1.45	14500	0.92	3.1	251	8	0.01	8	2	32	0.01	9.0	43	0.01
KL42-03	866	869	1.64	16400	0.76	3.7	257	9	0.01	6	1	45	0.01	8.8	38	0.01
KL42-03	869	872.1	4.3	43000	2.54	157	2300	1340	1480	5	810	43	12.8	1.0	56	0.34
KL42-03	872.1	875.2	0.6	6000	0.35	1	126	9	2	3	0.01	28	0.01	4.3	42	0.01
KL42-03	875.2	878.3	0.45	4500	0.37	1.7	1230	2390	3	5	1	10	0.3	5.0	28	0.01
KL42-03	878.3	881.4	0.415	4150	0.47	1	89	16	2	11	0.01	10	0.01	4.5	52	0.01
KL42-03	881.4	884.5	0.26	2600	0.33	1.2	126	10	3	8	0.01	17	0.2	3.0	48	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL42-03	884.5	887.6	0.088		880	0.15	7	138	303	15	52	1	6	3.4	2.1	122	0.01
KL42-03	887.6	890.9	0.038		380	0.04	0.01	187	45	3	56	0.01	6	0.3	1.8	75	0.01
KL42-03	890.9	893.9	0.091		910	0.08	1.6	79	71	7	90	0.01	4	2.4	0.8	97	0.01
KL42-03	893.9	896.9	0.042		420	0.03	0.6	96	10	2	8	0.01	11	0.2	1.0	24	0.01
KL42-03	896.9	899.9	0.059		590	0.03	0.9	59	7	2	20	0.01	6	0.3	0.7	30	0.01
KL42-03	899.9	902.9	0.062		620	0.02	0.5	32	11	3	16	0.01	3	0.3	2.3	96	0.01
KL42-03	902.9	905.9	0.0299		299	0.01	0.01	63	9	9	8	0.01	7	0.01	2.0	64	0.01
KL42-03	905.9	908.9	0.0276		276	0.16	0.01	37	24	4	18	0.01	2	0.6	1.0	47	0.01
KL42-03	908.9	911.9	0.048		480	1.11	14.2	104	130	12	132	1	4	1.5	3.5	129	0.01
KL42-03	911.9	914.9	0.062		620	0.12	39	203	318	13	130	1	2	3.2	1.0	133	0.01
KL42-03	914.9	917.9	0.049		490	0.04	0.8	36	26	5	127	0.01	2	0.2	0.7	144	0.01
KL42-03	917.9	920.9	0.106		1060	0.16	1.5	76	24	56	180	2	7	0.3	1.5	110	0.01
KL42-03	920.9	923.9	0.059		590	0.04	0.01	30	10	1	37	0.01	3	0.2	1.0	81	0.01
KL42-03	923.9	926.9	0.189		1890	0.03	1.4	38	11	1	82	9	4	0.3	2.3	39	0.01
KL42-03	926.9	929.9	0.07		700	0.02	0.5	18	10	0.01	14	0.01	0.01	0.2	1.3	16	0.01
KL42-03	929.9	932.9	4.11		41100	1.02	108	3400	14200	52	66	268	6	125	14.4	79	0.2
KL42-03	932.9	935.9	2.54		25400	0.44	12.8	1690	1580	8	46	80	11	3.4	10.0	46	0.01
KL42-03	935.9	938.9	1.95		19500	0.42	17.3	590	74	2	28	285	15	0.5	8.5	45	0.01
KL42-03	938.9	941.9	0.94		9400	0.16	3.2	189	18	1	154	80	10	0.01	3.3	17	0.01
KL42-03	941.9	944.9	0.073		730	0.02	1.2	54	29	3	17	0.01	0.01	0.5	1.0	12	0.01
KL42-03	944.9	947.9	0.443		4430	0.27	2.3	183	161	1	9	1	27	1	4.3	34	0.01
KL42-03	947.9	950.9	0.71		7100	0.46	3.4	109	11	2	7	3	24	0.3	6.1	28	0.01
KL42-03	950.9	953.9	0.94		9400	0.66	3.1	123	10	1	17	2	30	0.3	4.5	22	0.01
KL42-03	953.9	956.9	0.56		5600	0.44	2.3	103	10	7	6	0.01	16	0.4	4.8	24	0.01
KL42-03	956.9	959.9	0.32		3200	0.2	1.5	62	7	1	4	0.01	10	0.01	2.2	20	0.01
KL42-03	959.9	962.1	1.06		10600	1.12	6.3	333	11	2	5	7	48	2.1	9.0	43	0.01
KL42-03	962.1	964.3	0.34		3400	0.33	2.4	233	12	7	12	5	16	3.8	2.3	33	0.01
KL42-03	964.3	967.3	0.31		3100	0.72	1	68	10	0.01	4	1	17	0.01	3.8	27	0.01
KL42-03	967.3	969.6	0.97		9700	0.84	2.2	147	12	0.01	6	0.01	38	0.01	5.8	36	0.01
KL42-03	969.6	971.9	2.57		25700	1.16	6.2	317	10	1	4	0.01	54	0.01	6.0	25	0.01
KL42-03	971.9	973.5	0.164		1640	0.06	0.01	113	8	0.01	5	0.01	19	0.01	1.8	30	0.01
KL42-03	973.5	976.5	0.7		7000	0.2	1.6	121	11	0.01	5	0.01	19	0.3	5.3	33	0.01
KL42-03	976.5	979.2	0.35		3500	0.32	0.6	140	6	0.01	6	0.01	29	0.4	5.0	40	0.01
KL42-03	979.2	982.3	0.54		5400	0.16	1.5	164	46	2	58	0.01	13	0.6	5.0	78	0.01
KL42-03	982.3	985.1	0.181		1810	0.08	1	127	340	4	80	2	8	0.5	2.8	70	0.01
KL42-03	985.1	988.2	0.168		1680	0.05	0.8	34	11	0.01	34	0.01	5	0.01	2.1	60	0.01
KL42-03	988.2	991.2	0.219		2190	0.25	3.9	295	135	8	125	4	6	0.6	3.5	91	0.01
KL42-03	991.2	994.3	0.188		1880	0.14	2	74	83	7	66	2	8	1.2	3.3	71	0.01
KL42-03	994.3	997.4	0.185		1850	0.14	2.5	1120	144	14	32	2	6	1.5	3.5	58	0.01
KL42-03	997.4	1000.5	0.24		2400	0.13	1.9	70	10	2	89	1	9	0.2	4.0	85	0.01
KL42-03	1000.5	1003.6	0.3		3000	0.13	1.6	73	13	1	204	1	9	0.2	3.8	82	0.01
KL42-03	1003.6	1006.7	0.449		4490	0.07	2.3	191	70	0.01	137	1	27	0.6	9.4	87	0.01
KL42-03	1006.7	1009.8	0.152		1520	0.08	0.7	77	22	1	249	1	10	0.01	4.0	101	0.01
KL42-03	1009.8	1012.9	0.34		3400	0.54	8.2	415	520	16	187	11	8	1.5	2.8	55	0.01
KL42-03	1012.9	1015.3	0.161		1610	0.07	1.3	129	38	2	62	2	12	0.4	2.0	73	0.01
KL42-03	1015.3	1018.4	0.113		1130	0.02	2.3	212	189	13	164	2	3	3	3.0	129	0.01
KL42-03	1018.4	1022.2	0.182		1820	0.03	1.5	181	87	1	23	1	15	0.01	7.4	63	0.01
KL42-03	1022.2	1025.9	0.29		2900	0.12	0.8	72	20	2	6	0.01	10	0.01	3.8	17	0.01
KL42-03	1025.9	1028.9	0.106		1060	0.03	0.6	54	28	1	16	1	4	0.4	0.7	98	0.01
KL42-03	1028.9	1031.5	0.25		2500	0.07	1.3	61	34	1	13	1	7	0.4	5.3	22	0.01
KL42-03	1031.5	1034.9	0.8		8000	0.29	1.6	170	20	1	3	1	30	0.4	7.7	13	0.01
KL42-03	1034.9	1037.9	0.28		2800	0.11	2.9	212	42	3	47	2	19	0.6	3.3	18	0.01
KL42-03	1037.9	1039.7	0.086		860	0.03	0.6	124	13	0.01	5	0.01	30	0.5	1.3	22	0.01
KL42-03	1039.7	1041.4	0.157		1570	0.03	1.1	54	13	1	217	1	12	0.3	2.0	24	0.01
KL42-03	1041.4	1043.9	0.55		5500	0.26	1.7	88	29	2	8	0.01	11	0.4	3.8	21	0.01
KL42-03	1043.9	1046.9	0.3		3000	0.26	0.9	126	16	1	4	0.01	33	0.01	4.5	31	0.01
KL42-03	1046.9	1049.2	0.218		2180	0.12	0.01	124	14	1	6	0.01	25	0.5	2.5	17	0.01
KL42-03	1049.2	1052.3	0.079		790	0.09	2.4	440	600	2	14	2	15	0.9	3.6	62	0.01
KL42-03	1052.3	1054.5	0.058		580	0.06	0.01	116	18	0.01	7	1	34	0.01	0.9	24	0.01
KL42-03	1054.5	1057	0.142		1420	0.13	0.01	92	18	5	28	0.01	15	0.2	1.8	22	0.01
KL42-03	1057	1060.6	0.29		2900	0.18	1	85	34	2	16	0.01	16	0.5	4.5	22	0.01
KL42-03	1060.6	1062.6	0.54		5400	0.13	1.1	86	13	1	12	0.01	17	0.3	3.8	17	0.01
KL42-03	1062.6	1066.8	0.118		1180	0.05	0.5	76	114	0.01	9	0.01	4	0.3	2.3	16	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL42-03	1066.8	1070.6	0.185	1850	0.05	0.9	48	40	2	10	0.01	7	0.2	3.3	43	0.01
KL42-03	1070.6	1073	0.375	3750	0.27	5.5	200	260	0.01	172	1	19	1.1	4.5	16	0.01
KL42-03	1073	1075.6	0.31	3100	0.17	0.9	92	15	0.01	44	0.01	32	0.01	2.8	21	0.01
KL42-03	1075.6	1078.7	0.65	6500	0.58	1.7	147	11	0.01	4	5	19	0.01	3.3	15	0.01
KL42-03	1078.7	1081.5	0.468	4680	0.26	1	130	8	0.01	6	0.01	34	0.2	2.5	25	0.01
KL42-03	1081.5	1084.3	0.83	8300	0.41	1.2	108	7	1	4	1	18	0.4	5.6	17	0.01
KL42-03	1084.3	1087.8	0.461	4610	0.17	0.8	115	10	0.01	5	0.01	19	0.2	3.1	20	0.01
KL42-03	1087.8	1090	0.31	3100	0.08	0.6	107	10	0.01	3	0.01	28	0.2	2.3	20	0.01
KL42-03	1090	1093.2	1.9	19000	0.4	4.3	196	10	1	15	0.01	63	0.2	3.5	26	0.01
KL42-03	1093.2	1095.2	0.078	780	0.05	0.7	127	65	4	34	0.01	13	0.2	2.5	106	0.01
KL42-03	1095.2	1098	0.177	1770	0.05	1.3	346	212	1	181	1	10	0.3	4.8	164	0.01
KL42-03	1098	1100.9	0.193	1930	4.84	0.9	103	45	1	249	0.01	13	0.3	7.1	142	0.01
KL42-03	1100.9	1103.9	0.08	800	0.03	0.7	249	121	2	273	1	3	1	1.4	163	0.01
KL42-03	1103.9	1107	0.099	990	0.05	1	213	128	8	78	1	6	0.9	4.3	123	0.01
KL42-03	1107	1111	0.098	980	0.04	0.01	262	133	3	180	0.01	7	0.6	3.5	168	0.01
KL42-03	1111	1114.7	0.211	2110	0.02	0.8	136	82	2	127	1	8	0.4	4.3	160	0.01
KL42-03	1114.7	1117.8	0.166	1660	0.05	1	142	61	3	470	1	17	1.1	7.0	135	0.01
KL42-03	1117.8	1120.9	0.079	790	0.03	0.6	147	93	1	325	0.01	6	0.01	3.9	208	0.01
KL42-03	1120.9	1124	0.53	5300	0.17	1.7	103	28	3	110	1	16	0.4	8.5	148	0.01
KL42-03	1124	1127.1	0.407	4070	0.09	1.3	97	18	2	43	1	14	0.01	4.5	127	0.01
KL42-03	1127.1	1130.2	0.27	2700	0.05	0.6	106	28	3	121	0.01	8	0.2	2.0	93	0.01
KL42-03	1130.2	1133.3	0.33	3300	0.13	4.8	277	354	590	162	1	13	1.3	4.3	65	0.01
KL42-03	1133.3	1136.4	0.417	4170	0.13	6.4	254	50	670	100	1	7	1.6	3.3	112	0.01
KL42-03	1136.4	1139.5	0.24	2400	0.04	0.8	101	25	6	247	1	9	0.3	4.8	119	0.01
KL42-04	0	2.7	0.0101	101	0.01	0.5	172	83	6	8	0.01	0.01	0.9	0.6	18	0.01
KL42-04	2.7	5.7	0.0064	64	0.01	0.01	103	55	5	4	0.01	0.01	1.5	1.0	16	0.1
KL42-04	5.7	8.7	0.0036	36	0.01	0.01	125	81	7	3	0.01	0.01	1.6	0.8	15	0.01
KL42-04	8.7	11.7	0.0034	34	0.01	0.5	134	78	6	3	0.01	0.01	0.5	0.9	15	0.01
KL42-04	11.7	14.7	0.0054	54	0.01	0.01	168	107	8	2	0.01	0.01	2.2	2.5	6	0.01
KL42-04	14.7	17.7	0.0045	45	0.1	0.5	153	42	6	3	0.01	0.01	1.1	1.5	19	0.13
KL42-04	17.7	20.7	0.006	60	0.02	0.01	61	30	3	3	0.01	0.01	0.6	1.2	25	0.01
KL42-04	20.7	23.7	0.0086	86	0.01	0.01	69	21	1	3	0.01	0.01	0.5	0.9	19	0.01
KL42-04	23.7	26.7	0.0112	112	0.01	0.01	67	22	4	4	0.01	0.01	0.4	0.6	18	0.01
KL42-04	26.7	29.7	0.024	240	0.01	0.01	48	25	6	5	0.01	0.01	0.3	0.7	27	0.01
KL42-04	29.7	32.7	0.0244	244	0.01	0.8	91	56	9	6	0.01	0.01	1.1	0.6	26	0.01
KL42-04	32.7	35.7	0.0192	192	0.03	1	228	138	14	5	0.01	0.01	2.4	2.2	24	0.12
KL42-04	35.7	38.6	0.0098	98	0.02	0.7	76	55	10	6	0.01	0.01	1.6	1.5	19	0.16
KL42-04	38.6	41.7	0.008	80	0.01	0.01	54	26	7	3	0.01	0.01	0.7	1.2	17	0.13
KL42-04	41.7	44.7	0.0085	85	0.01	0.01	56	31	7	3	0.01	0.01	0.6	2.0	16	0.01
KL42-04	44.7	47.7	0.0126	126	0.02	0.9	351	104	7	5	0.01	0.01	1.4	1.5	20	0.11
KL42-04	47.7	50.1	0.0171	171	0.01	1.7	140	63	16	7	0.01	0.01	2.5	1.9	15	0.19
KL42-04	50.1	53.2	0.0106	106	0.01	0.5	51	36	6	3	0.01	0.01	0.8	1.3	16	0.01
KL42-04	53.2	56.3	0.0047	47	0.01	0.01	53	69	5	4	0.01	0.01	0.5	1.7	16	0.01
KL42-04	56.3	59.4	0.0017	17	0.01	0.01	38	30	1	2	0.01	0.01	1	1.1	17	0.01
KL42-04	59.4	62.5	0.0036	36	0.14	0.8	100	60	12	5	0.01	0.01	2.8	5.0	28	0.11
KL42-04	62.5	65.6	0.0043	43	0.18	0.6	82	52	16	6	0.01	0.01	2.2	3.6	26	0.11
KL42-04	65.6	68.7	0.31	3100	0.21	47	19900	17800	530	4	0.01	0.01	363	16.0	24	0.65
KL42-04	68.7	71.7	0.0102	102	0.29	1.4	388	370	38	3	0.01	0.01	14.5	4.1	27	0.49
KL42-04	71.7	74.7	0.0104	104	0.12	1.2	181	252	30	6	3	0.01	2.9	7.2	23	0.1
KL42-04	74.7	77.7	0.0045	45	0.34	0.7	229	123	41	4	0.01	0.01	6.4	2.6	24	0.26
KL42-04	77.7	80.7	0.043	430	0.16	12	6700	25000	38	5	6	0.01	15.9	290.0	30	0.01
KL42-04	80.7	83.7	0.0041	41	0.07	1.6	272	810	29	3	3	0.01	2.6	12.0	24	0.01
KL42-04	83.7	86.7	0.0036	36	0.08	0.01	164	186	19	2	1	0.01	1.7	2.4	16	0.01
KL42-04	86.7	89.7	0.0064	64	0.14	0.5	267	193	31	7	0.01	0.01	2.8	3.4	28	0.01
KL42-04	89.7	92.7	0.058	580	0.14	7	405	650	37	16	42	0.01	2.7	19.3	37	0.01
KL42-04	92.7	95.7	0.048	480	0.05	2.2	490	430	39	96	14	0.01	3.7	5.5	46	0.1
KL42-04	95.7	98.7	0.052	520	0.11	0.6	500	123	88	178	1	0.01	6.1	3.6	96	0.17
KL42-04	98.7	101.7	0.0251	251	0.42	0.6	1050	63	73	335	2	3	6.4	3.9	71	0.12
KL42-04	101.7	104.3	0.052	520	3.44	14.7	460	406	110	805	78	3	7.3	9.6	49	0.24
KL42-04	104.3	107.7	0.29	2900	2.12	67	10100	8200	350	440	250	4	45	58.0	186	2.5
KL42-04	107.7	110.2	0.0239	239	0.37	5.2	378	1110	29	801	8	0.01	2.3	3.8	198	0.14
KL42-04	110.2	113.7	0.0396	396	0.31	1.4	2010	660	96	236	1	0.01	3.4	2.3	85	0.2
KL42-04	113.7	116.7	0.0323	323	0.65	5.9	6800	4500	180	890	4	3	6.1	13.8	53	0.47

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL42-04	116.7	119.7	0.0395	395	0.81	15.2	3700	7500	68	450	3	0.01	7.3	6.8	55	0.52
KL42-04	119.7	122.7	0.025	250	0.3	7.3	1210	3500	34	250	0.01	0.01	5.1	6.2	302	0.23
KL42-04	122.7	127.1	0.0394	394	0.23	2.1	1630	660	69	1700	0.01	3	4.4	3.0	80	0.2
KL42-04	127.1	131.7	0.0193	193	0.56	11.1	9100	1600	320	342	28	3	10.1	8.3	96	0.26
KL42-04	131.7	134.7	0.012	120	0.49	4.1	3210	670	210	530	14	2	14.6	4.7	59	0.12
KL42-04	134.7	137.7	0.0097	97	0.08	1.9	410	152	76	480	5	0.01	9.3	1.6	33	0.01
KL42-04	137.7	140.9	0.092	920	0.21	2.6	3380	420	120	226	7	8	5.7	6.3	15	0.1
KL42-04	140.9	144	0.46	4600	0.2	7.9	13900	1200	810	273	16	19	26	13.2	17	0.75
KL42-04	144	146.7	0.066	660	0.32	3.3	4320	910	270	91	8	9	6.2	7.8	24	0.41
KL42-04	146.7	149	0.065	650	0.23	3.2	9300	500	210	139	18	9	6.9	7.8	28	0.27
KL42-04	149	152.7	0.0292	292	0.06	2	1790	880	110	30	5	3	4.3	4.6	22	0.11
KL42-04	152.7	155.4	0.035	350	0.05	2.8	2550	760	82	17	11	4	7.3	5.7	26	0.13
KL42-04	155.4	158	0.0157	157	0.06	1.7	940	470	24	14	7	2	2.6	4.7	23	0.11
KL42-04	158	160.9	0.054	540	0.1	3.9	4930	940	88	87	20	5	9.7	10.7	26	0.28
KL42-04	160.9	164.7	0.074	740	0.09	3.1	8700	880	180	294	12	6	8.1	14.4	33	0.24
KL42-04	164.7	167.4	0.075	750	0.42	4.6	17800	1540	200	83	32	15	4.3	11.3	38	0.2
KL42-04	167.4	170.6	0.051	510	0.12	5.6	15100	8500	120	37	5	3	11	10.6	35	0.12
KL42-04	170.6	173.7	0.097	970	0.4	9.2	9300	4600	130	60	23	8	10.3	20.4	35	0.26
KL42-04	173.7	175.7	0.138	1380	0.35	7.1	33200	1520	250	42	28	13	6.6	17.2	15	0.39
KL42-04	175.7	178.5	0.159	1590	1.97	13.2	33700	5500	490	103	282	28	10.2	26.0	33	1.49
KL42-04	178.5	180	0.066	660	0.74	4.2	23600	2600	290	57	18	17	7.5	16.8	16	0.85
KL42-04	180	182.4	0.55	5500	2.08	7.8	18200	410	510	83	22	51	8.7	21.5	72	0.14
KL42-04	182.4	185.7	0.36	3600	0.54	4.8	8900	192	130	1160	18	17	2.4	12.4	40	0.1
KL42-04	185.7	188.7	1.52	15200	0.86	16.7	22800	350	370	113	6	128	7.3	61.5	186	0.24
KL42-04	188.7	191.9	2.03	20300	1.42	13.1	34800	170	650	440	2	143	19.7	25.0	175	0.14
KL42-04	191.9	194.1	0.83	8300	1.54	6.9	14700	337	400	169	2	83	10.8	12.8	124	0.01
KL42-04	194.1	196.8	0.38	3800	1.32	4.5	15900	1450	480	100	1	50	13.7	13.0	110	0.01
KL42-04	196.8	199.9	1.81	18100	0.94	15.1	20800	200	250	296	2	119	8.4	23.5	106	0.12
KL42-04	199.9	202	4.25	42500	0.9	11.6	930	66	57	536	3	154	5.8	38.9	181	0.01
KL42-04	202	204.2	0.74	7400	0.16	0.9	460	45	35	770	2	21	1	10.3	57	0.01
KL42-04	204.2	206.7	0.42	4200	0.36	1.6	590	68	95	990	29	15	1.7	7.3	80	0.11
KL42-04	206.7	209.7	1.46	14600	0.4	5	1320	430	90	1910	33	22	2.2	11.5	105	0.26
KL42-04	209.7	212.7	2.02	20200	0.94	17.5	1980	300	220	1503	86	36	2.6	14.0	204	0.01
KL42-04	212.7	215	2.32	23200	1.78	37	9900	670	570	68	0.01	71	30	25.5	144	0.1
KL42-04	215	217.9	2.37	23700	1.12	39	11400	1570	640	1111	4	76	24	22.0	110	0.1
KL42-04	217.9	221	0.94	9400	0.55	5.3	2500	910	140	1720	6	23	3.7	10.0	68	0.01
KL42-04	221	224.1	0.53	5300	0.52	4.5	3180	880	240	840	7	24	4.5	8.8	37	0.01
KL42-04	224.1	227.2	1.98	19800	1.27	9	13700	2300	1060	1050	27	61	14.9	31.0	77	0.01
KL42-04	227.2	229.6	1.4	14000	1.72	10.7	49700	2700	770	535	23	82	32	76.0	68	0.12
KL42-04	229.6	232.2	1.57	15700	1.72	12.9	8900	1660	1770	152	4	79	38	17.5	77	0.11
KL42-04	232.2	235.8	0.83	8300	1.66	13.9	23000	3500	1410	640	26	76	26	36.6	64	0.1
KL42-04	235.8	238.9	0.104	1040	0.55	9.3	77800	9000	440	64	16	23	13.3	14.3	42	0.01
KL42-04	238.9	241.7	0.117	1170	1.17	10	41400	10000	500	154	27	21	13.5	45.4	63	0.32
KL42-04	241.7	244.8	0.13	1300	0.92	7.6	21200	9100	540	166	15	24	20.5	38.3	50	0.12
KL42-04	244.8	247.9	0.059	590	0.37	8.9	11700	14100	120	57	11	3	16.8	284.0	18	0.01
KL42-04	247.9	251	0.0304	304	0.22	0.01	850	270	39	20	1	3	2.4	7.3	13	0.1
KL42-04	251	254.1	0.063	630	1.33	5.5	4400	1870	500	166	17	15	38	32.7	35	0.5
KL42-04	254.1	257.2	0.089	890	0.25	1.8	2060	800	150	70	4	8	3.2	14.0	26	0.29
KL42-04	257.2	260.3	0.044	440	0.43	1.2	930	362	220	99	6	5	9.9	12.0	34	0.46
KL42-04	260.3	263.4	0.052	520	0.42	10.1	2740	2100	79	73	25	5	13.2	35.5	27	0.8
KL42-04	263.4	266.5	0.0394	394	0.41	5.1	1440	580	120	107	5	3	17.8	41.0	23	0.65
KL42-04	266.5	269.6	0.0318	318	0.31	3.9	4060	1590	63	56	24	5	4.8	0.0	25	0.42
KL42-04	269.6	272.7	0.0323	323	0.22	0.9	1750	368	69	30	5	12	3.1	14.3	17	0.17
KL42-04	272.7	275.7	0.07	700	0.4	6.7	6700	6700	200	97	17	7	11.8	36.0	28	0.47
KL42-04	275.7	278.7	0.069	690	0.44	4	7000	1850	67	116	18	7	8.9	32.0	31	0.66
KL42-04	278.7	281.7	0.053	530	0.32	3.4	5000	3000	100	116	7	8	22	31.5	28	0.6
KL42-04	281.7	284.7	0.22	2200	0.47	1.7	4960	273	160	140	2	20	12.4	11.2	38	0.66
KL42-04	284.7	287.7	0.063	630	1.1	0.6	840	85	180	176	1	5	13.9	6.0	88	1.06
KL42-04	287.7	290.7	0.168	1680	2.93	1.6	3380	79	240	315	4	10	12.3	10.5	187	1.82
KL42-04	290.7	293.7	0.062	620	0.67	0.7	1680	114	46	120	23	4	3.3	6.0	36	1.46
KL42-04	293.7	296.7	0.009	90	0.32	0.5	1020	720	38	11	0.01	2	8.1	16.2	27	2.08
KL42-04	296.7	299.7	0.0241	241	0.53	4	1100	840	100	22	2	3	20.1	6.0	31	2.73
KL42-04	299.7	302.7	0.0028	28	0.07	0.01	114	45	25	6	0.01	0.01	2.2	1.0	20	0.4

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL42-04	302.7	305.7	0.0138		138	0.2	0.6	334	148	160	11	2	0.01	14.5	3.0	23	1.69
KL42-04	305.7	308.7	0.0028		28	0.05	0.01	371	167	37	6	0.01	2	6	4.3	20	0.43
KL42-04	308.7	311.7	0.004		40	0.11	8.7	142	71	28	5	0.01	0.01	4.1	2.5	17	0.01
KL42-04	311.7	314.7	0.0042		42	0.15	1.4	102	37	29	6	0.01	2	2.6	1.3	24	0.01
KL42-04	314.7	317.7	0.21		2100	0.68	2.6	3590	48	50	26	10	14	3.5	6.3	26	0.01
KL42-04	317.7	320.7	0.085		850	1.09	3.1	5200	960	59	51	60	6	4.9	49.0	24	0.01
KL42-04	320.7	323.7	0.0085		85	0.29	3.9	4290	2800	33	13	4	3	9.4	80.3	21	0.01
KL42-04	323.7	326.7	0.0125		125	0.3	1	191	56	50	6	1	0.01	8.4	3.5	23	0.1
KL42-04	326.7	329.7	0.111		1110	1.35	1.8	383	37	21	18	55	4	1.7	3.8	22	0.01
KL42-04	329.7	332.7	0.0048		48	0.16	1.9	640	450	180	10	0.01	0.01	3.3	0.0	14	0.01
KL42-04	332.7	335.7	0.0037		37	0.05	0.6	271	198	36	6	0.01	3	1.1	1.3	23	0.01
KL42-04	335.7	338.7	0.0046		46	0.08	0.5	420	191	14	6	0.01	3	1.5	0.8	17	0.01
KL42-04	338.7	341.7	0.151		1510	0.35	2.2	470	410	48	660	5	3	2.3	4.5	25	0.15
KL42-04	341.7	344.7	0.46		4600	0.81	4.5	381	242	78	237	12	9	4.7	2.5	25	0.13
KL42-04	344.7	347.7	0.0128		128	0.08	0.01	210	46	24	12	1	2	1.6	0.0	21	0.01
KL42-04	347.7	350.7	0.0189		189	0.26	1.4	304	50	46	100	8	3	2.4	0.8	22	0.01
KL42-04	350.7	353.7	0.0092		92	0.06	0.01	137	22	160	13	0.01	3	4.2	0.0	20	0.01
KL42-04	353.7	356.7	0.0082		82	0.02	0.01	105	24	36	5	0.01	4	1.7	0.0	19	0.01
KL42-04	356.7	359.7	0.0195		195	0.05	0.01	198	19	130	78	0.01	4	3.4	0.0	21	0.1
KL42-04	359.7	362.7	0.0132		132	0.01	0.01	137	15	47	13	0.01	2	2.1	0.0	18	0.19
KL42-04	362.7	365.7	0.0076		76	0.01	0.01	123	41	59	14	0.01	2	13.5	0.0	16	0.2
KL42-05	0	4.7	0.011		110	0.05	1.7	610	248	9	4	0.01	0.01	1.3	1.6	14	0.28
KL42-05	4.7	7.5	0.0012		12	0.02	0.01	102	62	8	3	0.01	0.01	1	0.8	15	0.01
KL42-05	7.5	10	0.001		10	0.03	0.8	205	116	10	3	0.01	0.01	1.3	1.4	16	0.1
KL42-05	10	13.5	0.0009		9	0.01	0.5	174	75	9	4	0.01	0.01	1.3	1.5	17	0.01
KL42-05	13.5	16.9	0.0012		12	0.02	1.2	230	148	11	3	0.01	0.01	2.1	1.5	19	0.1
KL42-05	16.9	19.4	0.0011		11	0.01	0.7	162	64	13	2	0.01	0.01	0.8	1.0	16	0.01
KL42-05	19.4	22.7	0.0016		16	0.06	1.2	135	194	8	4	0.01	0.01	1.6	1.3	16	0.17
KL42-05	22.7	24.8	0.0018		18	0.06	0.5	221	109	7	3	0.01	0.01	1.3	2.1	17	0.14
KL42-05	24.8	26.8	0.0031		31	0.01	0.01	131	31	3	3	0.01	0.01	1.1	1.1	16	0.12
KL42-05	26.8	29.2	0.0022		22	0.02	0.01	109	56	10	3	0.01	0.01	1.8	2.1	20	0.1
KL42-05	29.2	32.8	0.0013		13	0.01	0.01	68	26	11	4	0.01	0.01	3.2	1.5	17	0.13
KL42-05	32.8	35.8	0.0014		14	0.01	0.01	120	44	10	4	0.01	0.01	3.1	1.5	37	0.1
KL42-05	35.8	38.8	0.0009		9	0.03	0.5	93	34	9	2	0.01	0.01	4.4	0.8	30	0.11
KL42-05	38.8	41.8	0.0012		12	0.01	0.01	74	26	12	4	0.01	0.01	1.7	0.9	34	0.1
KL42-05	41.8	44.8	0.0016		16	0.01	0.01	32	27	5	3	0.01	0.01	0.7	0.8	43	0.01
KL42-05	44.8	47.8	0.0021		21	0.01	0.01	28	16	12	4	0.01	0.01	0.6	1.4	33	0.01
KL42-05	47.8	50.8	0.0007		7	0.01	0.01	36	54	8	2	0.01	0.01	0.2	0.7	38	0.01
KL42-05	50.8	53.8	0.0016		16	0.01	0.01	55	34	7	0.01	0.01	0.01	1.1	0.5	33	0.1
KL42-05	53.8	56.8	0.0017		17	0.03	0.7	377	121	8	0.01	0.01	0.01	0.8	1.1	73	0.56
KL42-05	56.8	59	0.0008		8	0.07	0.7	282	152	7	0.01	0.01	0.01	1.2	1.2	59	0.49
KL42-05	59	61.2	0.0012		12	0.05	0.01	214	62	5	2	0.01	0.01	2	1.4	28	0.26
KL42-05	61.2	65.8	0.002		20	0.01	0.01	181	93	14	7	1	0.01	2.2	2.2	24	0.01
KL42-05	65.8	68.8	0.0039		39	0.01	0.5	82	102	12	23	0.01	0.01	3.1	1.4	58	0.01
KL42-05	68.8	71.8	0.0009		9	0.01	0.01	53	45	8	2	0.01	0.01	0.3	1.0	23	0.01
KL42-05	71.8	74.8	0.0013		13	0.01	0.01	800	254	11	3	0.01	2	1.3	2.1	18	0.12
KL42-05	74.8	77	0.001		10	0.01	0.01	219	85	16	3	0.01	0.01	1.8	1.4	26	0.01
KL42-05	77	80.1	0.0006		6	0.01	0.01	78	55	17	2	0.01	0.01	1.4	1.2	24	0.01
KL42-05	80.1	83.2	0.0021		21	0.01	1	353	193	17	3	0.01	0.01	13.7	1.5	18	0.18
KL42-05	83.2	86.3	0.0011		11	0.01	0.6	115	89	10	3	0.01	0.01	3.1	1.0	22	0.01
KL42-05	86.3	89.4	0.0008		8	0.01	0.01	56	50	11	0.01	0.01	0.01	0.8	1.2	23	0.1
KL42-05	89.4	92.5	0.0054		54	0.01	5.8	420	273	19	2	0.01	0.01	24	8.1	18	0.19
KL42-05	92.5	95.6	0.0017		17	0.02	1.2	247	153	12	3	0.01	0.01	12.2	2.7	20	0.14
KL42-05	95.6	98.7	0.0013		13	0.01	0.01	79	40	9	0.01	0.01	0.01	3.2	1.2	16	0.11
KL42-05	98.7	101.8	0.002		20	0.01	0.01	104	60	7	0.01	0.01	0.01	3.3	0.6	18	0.1
KL42-05	101.8	104.8	0.0013		13	0.01	0.01	78	37	11	0.01	0.01	0.01	2.4	1.5	20	0.11
KL42-05	104.8	107.8	0.0026		26	0.04	0.01	179	48	24	2	0.01	0.01	3.7	1.4	18	0.12
KL42-05	107.8	110.8	0.0033		33	0.03	0.01	150	131	21	3	0.01	0.01	2.9	1.9	22	0.13
KL42-05	110.8	113.8	0.0027		27	0.05	1.3	269	520	39	21	1	3	7.5	4.8	31	0.14
KL42-05	113.8	116.8	0.0018		18	0.05	1.3	188	258	24	4	0.01	0.01	3.3	1.9	25	0.1
KL42-05	116.8	119.8	0.0022		22	0.01	0.01	204	86	26	5	0.01	0.01	3.8	1.4	36	0.1
KL42-05	119.8	122.8	0.0054		54	0.04	0.6	440	131	58	2	1	0.01	3.1	3.9	38	0.1
KL42-05	122.8	125.8	0.0037		37	0.11	1	790	340	53	3	1	2	20.1	4.8	47	0.36

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL42-05	125.8	128.8	0.0021		21	0.16	1.2	670	520	45	43	0.01	0.01	10.5	1.0	62	0.17
KL42-05	128.8	131.8	0.0027		27	0.07	0.8	1010	293	45	26	0.01	0.01	4	1.4	100	0.11
KL42-05	131.8	135	0.0104		104	0.1	1.5	1330	540	49	36	0.01	5	4	2.5	69	0.19
KL42-05	135	137.8	1.61		16100	1.34	122	32600	39000	1910	43	146	55	208	68.5	154	6.94
KL42-05	137.8	140.8	0.3		3000	0.78	41	6700	14500	800	3700	80	36	382	32.0	188	2.8
KL42-05	140.8	143.8	0.123		1230	0.53	29.8	17700	15000	300	80	5	3	153	29.0	223	4.85
KL42-05	143.8	146.8	0.0067		67	0.5	11.4	2100	7100	45	25	5	0.01	3.8	7.2	215	0.5
KL42-05	146.8	149.8	0.017		170	0.48	11	1290	3510	77	28	2	0.01	17	4.3	188	0.3
KL42-05	149.8	152.8	0.084		840	0.43	29.6	1300	3910	160	15	42	2	45	5.8	205	0.28
KL42-05	152.8	155.7	0.0059		59	0.28	11.8	1240	6000	75	10	4	2	5.8	3.0	243	0.24
KL42-05	155.7	158.8	0.0049		49	0.18	3	2610	1350	27	20	0.01	3	4	3.0	183	0.28
KL42-05	158.8	161.7	0.0035		35	0.09	2.1	1870	670	20	96	2	0.01	2.8	3.3	97	0.16
KL42-05	161.7	164.5	0.002		20	0.09	4.8	1660	600	25	105	8	0.01	2	2.8	156	0.22
KL42-05	164.5	166.7	0.0046		46	0.33	6	4440	1630	53	113	7	3	3.8	5.3	123	0.42
KL42-05	166.7	169.3	0.0236		236	0.39	5.8	3340	1710	80	496	42	2	7.5	8.8	125	0.44
KL42-05	169.3	173.8	0.0094		94	0.59	5.2	8000	2200	150	520	1	2	7.8	4.5	70	0.58
KL42-05	173.8	179.8	0.0047		47	0.22	2.3	1520	960	99	654	1	3	10	3.7	109	0.11
KL42-05	179.8	185.8	0.0336		336	0.29	9.2	2690	730	230	575	2	4	40	6.3	97	0.2
KL42-05	185.8	188.7	0.59		5900	0.84	12.6	24000	302	1910	180	130	88	67	30.5	88	0.4
KL42-05	188.7	191.6	0.279		2790	0.9	9.2	3210	790	1230	747	170	20	57	41.5	130	0.34
KL42-05	191.6	195.1	0.264		2640	0.33	3.8	2180	323	800	102	48	15	48	10.5	45	0.19
KL42-05	195.1	198.9	0.06		600	0.11	3.2	4570	740	140	48	29	6	75	12.3	39	0.2
KL42-05	198.9	201.9	0.0138		138	0.22	2.4	2990	510	60	25	30	0.01	6.5	7.0	23	0.17
KL42-05	201.9	204.6	0.0079		79	0.23	1.9	1650	372	56	48	9	0.01	11.7	4.5	19	0.11
KL42-05	204.6	206.8	0.0267		267	0.5	2.4	3090	680	220	20	41	0.01	43	5.8	20	0.13
KL42-05	206.8	209.8	0.058		580	0.17	3.4	3260	970	170	35	15	3	108	7.2	25	0.16
KL42-05	209.8	212.8	0.0227		227	0.23	4.2	3050	1110	88	15	88	4	35	10.5	35	0.26
KL42-05	212.8	217.8	0.0066		66	0.04	0.7	500	192	14	8	2	0.01	1.6	3.4	24	0.01
KL42-05	217.8	220.8	0.0061		61	0.04	1.3	910	181	16	45	18	0.01	3	5.3	21	0.1
KL42-05	220.8	223.6	0.0088		88	0.03	1.1	335	130	16	76	7	0.01	1.8	6.4	24	0.01
KL42-05	223.6	226.6	0.0123		123	0.03	1.8	720	490	22	46	7	0.01	4	3.6	22	0.01
KL42-05	226.6	230.2	0.05		500	0.1	7.2	11000	8900	71	35	6	3	13.6	46.0	24	0.2
KL42-05	230.2	233.5	0.0229		229	0.1	1.2	840	339	90	79	5	0.01	14.6	5.7	20	0.01
KL42-05	233.5	236.8	0.084		840	0.24	3.6	4960	670	380	137	20	8	65	8.0	33	0.3
KL42-05	236.8	239.1	0.0078		78	0.24	1.6	2360	198	130	93	15	0.01	8.5	6.5	35	0.2
KL42-05	239.1	242.6	0.113		1130	0.31	21.4	7000	5500	340	393	140	4	44	23.3	23	0.24
KL42-05	242.6	245.4	0.0143		143	0.2	1	930	265	32	28	36	0.01	15.2	4.7	12	0.12
KL42-05	245.4	248.2	0.067		670	0.11	1.5	1720	230	160	38	9	3	66	5.2	15	0.11
KL42-05	248.2	251.8	0.0112		112	0.05	0.01	520	75	36	24	4	0.01	7	1.9	11	0.1
KL42-05	251.8	254.2	0.0043		43	0.01	0.01	480	62	5	14	4	0.01	3.4	1.4	10	0.01
KL42-05	254.2	256.7	0.0033		33	0.02	0.01	570	69	10	27	1	3	2	1.2	12	0.01
KL42-05	256.7	259.6	0.0119		119	0.07	1.1	3320	540	46	25	14	17	16	7.1	24	0.12
KL42-05	259.6	262	0.0122		122	0.07	1.2	3240	710	55	38	13	2	30	4.3	23	0.1
KL42-05	262	265.6	0.153		1530	0.29	2.8	33200	167	200	94	17	170	19.8	12.3	25	0.18
KL42-05	265.6	269.8	0.0103		103	0.04	0.01	1140	115	16	72	3	3	9.1	1.9	11	0.01
KL42-05	269.8	272.3	0.0054		54	0.01	0.7	880	92	6	17	3	0.01	0.9	1.0	10	0.01
KL42-05	272.3	274.9	0.0047		47	0.01	0.7	590	207	11	41	2	0.01	6.5	2.0	9	0.01
KL42-05	274.9	277.9	0.0108		108	0.02	1.4	1320	145	8	40	12	2	2.3	3.2	10	0.01
KL42-05	277.9	281.8	0.0051		51	0.02	0.5	710	147	7	64	0.01	2	3.5	1.7	8	0.1
KL42-05	281.8	285.3	0.296		2960	0.24	4.7	3740	1330	860	38	2	6	30	8.7	20	0.24
KL42-05	285.3	288	0.0148		148	0.03	0.5	670	72	21	116	3	0.01	2.3	2.2	11	0.01
KL42-05	288	291	0.0212		212	0.02	0.6	850	65	48	78	3	3	1.9	2.1	14	0.01
KL42-05	291	294	0.0317		317	0.03	0.6	1450	112	46	281	6	2	5.1	4.3	13	0.1
KL42-05	294	297.1	0.008		80	0.02	0.01	470	66	18	87	6	2	1	1.8	15	0.1
KL42-05	297.1	299.9	0.117		1170	0.08	1.9	4210	343	330	155	30	2	12	2.0	14	0.17
KL42-05	299.9	302	0.0031		31	0.01	2.4	1020	310	15	38	16	0.01	2.3	2.0	12	0.01
KL42-05	302	305.8	0.0204		204	0.04	2	3270	740	31	36	28	2	6.4	5.5	9	0.11
KL42-05	305.8	308.8	0.052		520	0.11	1.4	3010	400	130	45	20	2	18.7	8.8	20	0.1
KL42-05	308.8	311.8	0.007		70	0.03	0.7	1850	540	16	18	2	0.01	1.8	6.3	13	0.1
KL42-05	311.8	314.4	0.0387		387	0.03	1.3	890	402	76	12	12	0.01	18.9	5.0	10	0.1
KL42-05	314.4	317.2	0.037		370	0.05	1.2	1060	610	60	14	1	3	13.7	2.3	11	0.13
KL42-05	317.2	319.4	0.042		420	0.05	0.8	1410	480	60	6	0.01	0.01	9	6.7	12	0.1
KL42-05	319.4	323.2	0.034		340	0.06	1.5	2400	1100	42	8	1	2	7.2	11.5	11	0.1

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL42-05	323.2	326.3	0.0133		133	0.22	0.9	1300	480	34	38	8	0.01	4.4	5.0	12	0.11
KL42-05	326.3	329.4	0.0316		316	0.05	1.3	1650	1350	47	15	1	0.01	5.7	8.0	17	0.1
KL42-05	329.4	332.5	0.0108		108	0.01	0.8	700	900	29	9	3	2	1.5	2.8	20	0.1
KL42-05	332.5	335.6	0.0385		385	0.08	15.8	14900	20200	36	48	7	3	11.3	89.0	20	0.11
KL42-05	335.6	338.7	0.053		530	0.09	20.6	11500	25900	68	18	16	2	40.5	54.0	20	0.12
KL42-05	338.7	341.8	0.0167		167	0.04	0.6	520	221	27	16	5	0.01	5.7	3.0	12	0.01
KL42-05	341.8	345.3	0.0074		74	0.05	0.6	345	430	21	6	1	2	2.8	5.5	9	0.1
KL42-05	345.3	348.5	0.0066		66	0.05	0.6	1120	406	23	7	0.01	0.01	4.4	2.8	8	0.16
KL42-05	348.5	350.8	0.107		1070	0.14	0.9	630	229	170	12	2	4	14.3	9.0	17	0.1
KL42-05	350.8	353.8	0.089		890	0.14	0.7	910	185	130	4	1	5	11.1	12.5	37	0.01
KL42-05	353.8	356.8	0.276		2760	0.4	1.1	385	76	74	9	5	4	4.1	11.3	14	0.01
KL42-05	356.8	359.3	1.37		13700	2	3.2	219	29	90	18	2	13	2.6	16.0	36	0.1
KL42-05	359.3	362.8	1.41		14100	1.55	3.7	214	82	29	19	1	18	0.2	22.5	31	0.01
KL42-05	362.8	365.8	0.91		9100	1.07	3.1	315	23	47	29	1	28	3.1	19.4	29	0.01
KL42-05	365.8	368.1	0.97		9700	0.61	2.4	730	65	88	17	2	16	3.6	10.0	31	0.11
KL42-05	368.1	370.8	1.99		19900	0.56	2.2	18000	33	32	1740	4	96	3.8	20.0	50	0.01
KL42-05	370.8	374.8	0.136		1360	0.07	0.01	460	86	46	830	0.01	6	5.6	4.3	116	0.1
KL42-05	374.8	377.8	0.133		1330	0.41	1.3	2490	580	250	2700	0.01	11	26	14.1	135	0.25
KL42-05	377.8	380.8	0.091		910	0.43	0.9	1470	294	200	1600	1	12	9.3	15.2	96	0.1
KL42-05	380.8	383.8	0.367		3670	0.21	1	1640	189	380	182	0.01	9	8.7	8.8	72	0.1
KL42-05	383.8	387.8	0.404		4040	0.3	1.1	400	38	30	31	4	10	1.1	6.5	29	0.01
KL42-05	387.8	389.8	1.24		12400	0.75	3.2	600	12	23	30	1	28	0.6	14.0	24	0.01
KL42-05	389.8	392.7	0.519		5190	0.61	1	155	14	22	15	4	9	0.4	6.8	19	0.01
KL42-05	392.7	395.4	0.54		5400	0.39	1.2	178	23	70	317	1	14	1.1	4.0	44	0.01
KL42-05	395.4	398.5	0.84		8400	0.55	2.6	235	15	27	64	14	29	2.6	6.3	22	0.1
KL42-05	398.5	400.8	0.58		5800	0.37	2.4	1670	1680	34	22	2	22	4.3	11.9	27	0.1
KL42-05	400.8	404.8	0.95		9500	0.46	1.8	192	42	27	14	1	31	2.8	8.5	20	0.01
KL42-05	404.8	407.8	0.55		5500	0.23	1.2	205	86	27	13	0.01	16	3.4	7.0	15	0.01
KL42-05	407.8	410.2	0.525		5250	0.21	1.9	580	710	55	32	1	17	3.8	7.4	20	0.01
KL42-05	410.2	413.8	0.63		6300	0.33	1.9	210	31	24	9	1	20	3.1	13.8	32	0.01
KL42-05	413.8	416.8	0.64		6400	0.13	2.9	325	117	23	30	0.01	15	1.8	9.3	19	0.01
KL42-05	416.8	419.8	0.85		8500	0.64	3.1	347	33	25	21	1	50	2.4	12.8	28	0.01
KL42-05	419.8	422.8	0.22		2200	0.24	1.2	690	29	24	19	1	24	2.6	5.8	22	0.01
KL42-05	422.8	425.8	0.515		5150	0.53	1.5	2540	14	24	5	6	32	2.5	8.3	20	0.01
KL42-05	425.8	428.7	0.69		6900	0.36	2	162	14	11	10	0.01	7	1	5.3	18	0.12
KL42-05	428.7	431.5	0.31		3100	0.25	2.1	10400	16	13	6	14	58	2.1	4.9	35	0.01
KL42-05	431.5	434.1	0.31		3100	0.19	1.1	970	35	9	36	1	13	1.5	4.2	18	0.01
KL42-05	434.1	437.2	0.088		880	0.05	0.6	101	25	3	11	0.01	4	0.6	1.5	12	0.01
KL42-05	437.2	440.1	0.24		2400	0.12	1	96	55	17	107	3	3	0.4	2.5	18	0.01
KL42-05	440.1	443.2	1.13		11300	0.53	2.6	480	18	6	7	5	46	3	6.5	22	0.01
KL42-05	443.2	446.8	0.65		6500	0.31	1.7	870	25	23	0.01	3	46	3.3	8.8	21	0.01
KL42-05	446.8	449.4	1.05		10500	0.54	2.1	860	110	130	27	0.01	32	7	11.5	21	0.01
KL42-05	449.4	452.5	0.279		2790	0.16	0.7	2290	34	32	14	0.01	40	2.2	5.5	21	0.01
KL42-05	452.5	455	0.126		1260	0.06	0.6	430	216	34	41	6	12	3.4	5.3	20	0.01
KL42-05	455	457.7	0.088		880	0.05	0.7	294	147	52	238	7	7	3.3	4.3	40	0.01
KL42-05	457.7	460.4	0.222		2220	0.33	1	3950	105	67	28	14	36	5.6	8.3	24	0.01
KL42-05	460.4	464.8	0.459		4590	0.43	1.5	1280	137	37	0.01	1	14	3.1	9.5	18	0.01
KL42-05	464.8	467.8	0.61		6100	0.4	2.2	338	66	43	3	3	26	0.8	28.4	43	0.01
KL42-05	467.8	470.8	0.77		7700	0.45	2.6	313	27	40	2	1	20	0.6	45.8	44	0.01
KL42-05	470.8	473.8	0.92		9200	0.96	1.5	147	9	10	3	0.01	15	0.3	8.3	24	0.01
KL42-05	473.8	476.8	1.06		10600	1.05	1.1	175	51	16	2	0.01	14	1.1	6.9	24	0.01
KL42-05	476.8	479.8	0.501		5010	0.57	0.8	172	42	15	2	0.01	11	1.2	4.3	67	0.01
KL42-05	479.8	482.8	1.65		16500	1.51	13.1	6700	1360	65	5	0.01	49	14	19.0	41	0.23
KL42-05	482.8	485.8	0.77		7700	0.61	3.2	12700	133	51	3	5	82	5.6	16.5	21	0.01
KL42-05	485.8	488.8	1.08		10800	1.2	1.8	960	66	20	4	0.01	40	3.2	8.5	27	0.01
KL42-05	488.8	491.8	1.45		14500	1.15	2	1570	32	4	4	0.01	70	1	9.5	28	0.01
KL42-05	491.8	494.8	0.33		3300	0.11	0.8	1400	190	29	3	1	17	1.4	12.8	38	0.01
KL42-05	494.8	497.8	1.46		14600	0.42	3.5	1820	390	60	2	2	40	2.5	35.5	50	0.01
KL42-05	497.8	499.2	0.63		6300	0.28	2.7	430	175	32	5	1	23	1.3	11.8	39	0.01
KL42-05	499.2	502.9	2.15		21500	0.98	7.2	2600	1240	27	8	9	72	3.1	35.0	118	0.01
KL42-05	502.9	504.2	0.23		2300	0.07	1	48	27	32	161	3	7	3.7	16.0	100	0.01
KL42-05	504.2	506.8	0.448		4480	0.07	0.9	44	21	51	23	5	12	0.8	39.0	117	0.01
KL42-05	506.8	510	0.6		6000	0.13	1.9	66	36	98	224	10	9	2.3	27.2	112	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL42-05	510	513	0.463		4630	0.16	1.8	31	17	12	31	8	18	0.5	18.5	119	0.01
KL42-05	513	515.6	0.31		3100	0.27	1.8	33	15	12	26	7	11	0.4	15.9	160	0.01
KL42-05	515.6	518.7	0.3		3000	0.13	1.2	30	14	8	20	5	9	0.5	18.0	187	0.01
KL42-05	518.7	521.8	0.3		3000	0.15	1.1	29	19	9	12	3	9	0.2	17.3	131	0.01
KL42-05	521.8	524.8	0.29		2900	0.13	1.3	33	17	10	11	7	11	0.3	10.5	138	0.01
KL42-05	524.8	527.8	0.168		1680	0.1	1.2	35	40	8	30	3	8	0.4	19.5	169	0.01
KL42-05	527.8	530.7	0.26		2600	0.22	1.4	34	12	8	11	3	10	0.3	13.3	112	0.01
KL42-05	530.7	533	0.397		3970	0.22	1.6	45	39	9	16	4	9	0.3	12.0	96	0.01
KL42-05	533	536.1	0.21		2100	0.13	1	72	38	8	16	3	6	0.2	8.0	65	0.01
KL42-05	536.1	539.8	0.23		2300	0.11	1.4	55	21	7	28	5	7	0.3	4.3	67	0.01
KL42-05	539.8	542.8	0.132		1320	0.1	0.7	144	27	6	15	1	4	0.2	2.5	66	0.01
KL42-05	542.8	545.8	0.137		1370	0.07	0.6	44	13	1	8	1	5	0.01	1.5	63	0.01
KL42-05	545.8	548.8	0.107		1070	0.07	0.01	32	11	2	19	0.01	4	0.01	1.3	72	0.01
KL42-05	548.8	551.8	0.11		1100	0.07	0.5	38	12	3	13	0.01	5	0.3	4.0	53	0.1
KL42-05	551.8	554.8	0.099		990	0.09	0.8	460	35	3	22	0.01	4	0.3	1.8	59	0.01
KL42-05	554.8	557.8	0.215		2150	0.16	0.7	45	11	2	230	0.01	4	0.01	2.5	62	0.01
KL42-05	557.8	560.8	0.26		2600	0.12	2	168	124	4	63	1	8	0.4	1.8	78	0.01
KL42-05	560.8	563.8	0.25		2500	0.14	0.9	101	32	4	24	0.01	4	0.2	2.3	52	0.01
KL42-05	563.8	566.8	0.59		5900	0.5	1	45	14	2	42	0.01	7	0.01	6.9	51	0.01
KL42-05	566.8	569	0.58		5800	0.35	1.6	67	42	7	29	2	14	0.5	12.3	67	0.01
KL42-05	569	572.8	0.524		5240	0.07	1.4	198	108	9	33	1	4	1	4.5	270	0.01
KL42-05	572.8	575.8	0.391		3910	0.25	2.4	97	106	2	71	1	3	0.9	4.3	234	0.01
KL42-05	575.8	578.8	0.33		3300	0.22	1	162	25	4	13	0.01	13	0.4	3.3	187	0.01
KL42-05	578.8	581.8	0.25		2500	0.1	2.7	129	74	3	42	3	3	0.5	3.5	238	0.1
KL42-05	581.8	584.8	0.445		4450	0.7	14.2	279	107	74	968	16	11	18	12.0	246	0.58
KL42-05	584.8	587.8	0.474		4740	0.11	2.2	67	65	19	28	0.01	3	5.8	3.0	236	0.01
KL42-05	587.8	590.8	0.8		8000	0.14	3.8	32	29	2	36	2	7	1	4.0	132	0.01
KL42-05	590.8	593.8	0.496		4960	0.13	1.9	79	94	2	27	0.01	8	1.7	4.8	184	0.01
KL42-05	593.8	596.8	0.399		3990	0.23	1.8	152	90	23	33	0.01	7	8	3.5	216	0.13
KL42-05	596.8	599.8	0.31		3100	0.22	2.2	261	141	7	59	9	7	1.6	3.3	185	0.01
KL42-05	599.8	602.8	0.24		2400	0.15	1.5	109	84	2	14	1	5	1.3	1.8	203	0.01
KL42-05	602.8	605.8	0.119		1190	0.06	1.4	31	38	4	60	1	7	0.9	1.5	304	0.01
KL42-05	605.8	608.8	0.23		2300	0.1	2.1	31	22	7	56	1	7	0.8	4.8	318	0.01
KL42-05	608.8	611.8	0.109		1090	0.09	1.4	55	47	1	27	0.01	5	0.6	1.8	269	0.01
KL42-05	611.8	614.8	0.158		1580	0.05	1.4	460	870	4	827	0.01	7	1.5	3.5	386	0.01
KL42-05	614.8	617.8	0.175		1750	0.17	1.3	165	42	4	180	1	7	1.7	3.6	332	0.01
KL42-05	617.8	620.8	0.201		2010	0.03	0.6	185	59	44	78	0.01	11	2.5	1.8	413	0.01
KL42-05	620.8	623.8	0.169		1690	0.02	0.6	46	32	24	76	0.01	16	2.6	2.3	295	0.01
KL42-05	623.8	626.8	0.314		3140	0.03	1.4	30	25	0.01	183	0.01	5	1.4	2.3	220	0.01
KL42-05	626.8	629	0.29		2900	0.02	0.9	37	19	1	71	0.01	12	3.1	2.1	215	0.01
KL42-06	0	3.1	0.0285		285	0.02	3.5	810	243	8	2	0.01	0.01	1.6	1.7	16	0.2
KL42-06	3.1	6.6	0.065		650	0.04	6.3	1910	530	16	4	0.01	0.01	3.4	2.6	18	0.23
KL42-06	6.6	9.7	0.0101		101	0.04	0.8	120	101	5	2	0.01	0.01	1.2	0.0	19	0.01
KL42-06	9.7	12.2	0.0213		213	0.07	0.7	167	87	6	3	0.01	0.01	1.2	0.0	22	0.1
KL42-06	12.2	15	0.0127		127	0.04	0.6	131	63	3	2	0.01	0.01	1.1	0.0	19	0.11
KL42-06	15	18.1	0.0027		27	0.02	0.5	79	57	5	3	0.01	0.01	0.8	0.0	19	0.01
KL42-06	18.1	21.1	0.0026		26	0.03	0.7	100	55	4	2	0.01	0.01	1.2	1.0	18	0.1
KL42-06	21.1	24.3	0.0039		39	0.03	0.7	126	49	9	4	0.01	0.01	2.1	0.5	20	0.18
KL42-06	24.3	27.1	0.0022		22	0.03	0.7	89	48	4	0.01	0.01	0.01	1.1	0.0	17	0.11
KL42-06	27.1	30.1	0.002		20	0.02	0.6	72	57	3	2	0.01	0.01	1.4	0.0	17	0.12
KL42-06	30.1	33.3	0.0039		39	0.01	0.6	110	69	5	3	0.01	0.01	1.5	0.0	18	0.1
KL42-06	33.3	36.6	0.0026		26	0.02	0.8	113	76	5	0.01	0.01	0.01	1.2	0.8	19	0.1
KL42-06	36.6	38.9	0.0016		16	0.01	1	172	80	4	0.01	0.01	0.01	0.8	0.0	17	0.1
KL42-06	38.9	42.6	0.001		10	0.03	0.9	210	126	3	3	0.01	0.01	1	0.0	20	0.12
KL42-06	42.6	45.6	0.0014		14	0.05	2	590	185	8	3	0.01	0.01	2.2	1.0	20	0.11
KL42-06	45.6	48.1	0.0017		17	0.05	1.5	460	192	8	2	0.01	0.01	1.3	1.9	17	0.49
KL42-06	48.1	51.7	0.0047		47	0.02	0.8	193	68	3	3	0.01	0.01	0.5	0.8	18	0.16
KL42-06	51.7	55.5	0.0026		26	0.02	1.2	325	143	4	0.01	0.01	0.01	1.4	0.8	18	0.49
KL42-06	55.5	58.8	0.002		20	0.01	0.9	201	79	3	2	0.01	0.01	0.5	0.8	17	0.15
KL42-06	58.8	62.4	0.0011		11	0.01	1.1	176	64	1	3	0.01	0.01	0.6	0.5	20	0.16
KL42-06	62.4	64.9	0.0093		93	0.02	0.7	96	50	4	6	0.01	0.01	0.3	2.2	21	0.01
KL42-06	64.9	67.3	0.0098		98	0.01	0.6	43	33	1	4	0.01	0.01	0.2	0.8	21	0.01
KL42-06	67.3	69.9	0.0081		81	0.01	1	160	62	2	2	0.01	0.01	0.5	0.5	17	0.1

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL42-06	69.9	72.4	0.0015		15	0.02	1.5	281	115	5	2	0.01	0.01	0.5	1.2	18	0.3
KL42-06	72.4	76.9	0.0015		15	0.01	0.7	152	75	6	0.01	0.01	0.01	0.6	1.9	21	0.13
KL42-06	76.9	80	0.0012		12	0.01	1.1	234	85	4	0.01	0.01	0.01	0.6	1.0	21	0.22
KL42-06	80	83.1	0.002		20	0.02	1	265	112	9	3	0.01	0.01	0.8	1.3	21	0.2
KL42-06	83.1	86.4	0.0033		33	0.03	1.2	800	286	21	3	0.01	0.01	1.7	0.5	25	0.22
KL42-06	86.4	89.1	0.002		20	0.03	0.8	380	145	4	2	0.01	0.01	0.7	1.0	23	0.1
KL42-06	89.1	92.8	0.0042		42	0.08	1	480	250	9	2	0.01	0.01	1	1.0	23	0.2
KL42-06	92.8	95.7	0.33		3300	0.08	1.9	630	354	33	3	2	0.01	8.7	1.2	26	0.17
KL42-06	95.7	98.4	1.12		11200	0.15	6.1	2600	1870	72	2	5	0.01	24	1.5	31	0.42
KL42-06	98.4	101.4	0.0381		381	0.13	4.9	3300	2900	51	2	4	0.01	3.6	3.8	22	0.57
KL42-06	101.4	104.8	0.0309		309	0.08	3.5	1920	1380	29	10	3	0.01	3	2.8	24	0.62
KL42-06	104.8	108.2	0.0055		55	0.1	2.8	1930	980	20	2	0.01	0.01	4	2.3	26	0.84
KL42-06	108.2	111.4	0.0104		104	0.11	1.1	750	272	16	7	0.01	0.01	2.1	0.5	28	0.4
KL42-06	111.4	114.8	0.0033		33	0.06	0.9	530	230	7	2	0.01	0.01	1.8	0.8	25	0.21
KL42-06	114.8	117.6	0.0024		24	0.02	0.01	145	63	5	3	0.01	0.01	0.9	1.5	27	0.01
KL42-06	117.6	120.2	0.0027		27	0.01	0.5	152	80	7	3	0.01	0.01	0.4	0.0	25	0.11
KL42-06	120.2	123	0.0152		152	0.24	2.7	1480	1200	19	3	3	0.01	0.9	1.2	31	0.26
KL42-06	123	125.4	0.0112		112	0.6	2.2	1230	690	20	3	0.01	0.01	1.6	1.0	41	0.13
KL42-06	125.4	128.4	0.0338		338	0.83	4.3	1980	1180	31	2	4	0.01	3.3	2.3	35	0.23
KL42-06	128.4	132.1	4.01		40100	2.03	37	1760	1440	920	4	52	0.01	230	3.5	286	1.04
KL42-06	132.1	134.1	5.79		57900	2.67	38	610	550	1770	5	62	2	355	12.0	145	1.53
KL42-06	134.1	137.7	0.0332		332	0.15	3.8	1880	960	31	0.01	0.01	0.01	5.5	3.3	33	0.17
KL42-06	137.7	140.4	0.0203		203	0.11	6	4800	1920	42	2	0.01	0.01	4.2	2.8	33	0.28
KL42-06	140.4	143.4	0.52		5200	0.23	135	40200	39100	1330	0.01	272	0.01	86	17.0	47	4.53
KL42-06	143.4	146.3	0.0278		278	0.18	19.6	14500	9700	69	3	3	0.01	11.4	6.3	35	1.07
KL42-06	146.3	149.4	0.0218		218	0.08	7.6	5100	3200	53	2	1	0.01	6.8	3.0	34	0.51
KL42-06	149.4	152.4	0.0102		102	0.04	2.5	2420	1290	35	2	0.01	0.01	4	1.1	30	0.31
KL42-06	152.4	155.9	0.0033		33	0.04	1.4	1380	590	26	0.01	0.01	0.01	3.3	1.3	27	0.24
KL42-06	155.9	158.4	0.004		40	0.13	2.8	2500	800	20	4	0.01	0.01	5.5	3.8	28	0.39
KL42-06	158.4	161.4	0.0063		63	0.09	2.5	1380	530	15	5	0.01	0.01	7.2	2.5	23	0.27
KL42-06	161.4	164.3	0.0203		203	0.27	1.8	860	370	22	2	0.01	0.01	4.1	2.6	31	0.1
KL42-06	164.3	167.4	0.0072		72	0.14	1.6	910	298	24	3	0.01	0.01	7.1	3.3	28	0.25
KL42-06	167.4	170.4	0.0073		73	0.17	1.4	950	365	27	2	0.01	0.01	8.1	2.0	29	0.51
KL42-06	170.4	173.4	0.0081		81	0.17	1.9	1500	590	19	4	0.01	0.01	4.7	2.0	19	0.84
KL42-06	173.4	176.9	0.39		3900	0.21	2.6	990	670	43	3	3	0.01	10.7	3.0	19	0.27
KL42-06	176.9	180.1	0.0345		345	0.12	19.5	9900	13900	33	3	0.01	0.01	55	19.0	14	2.16
KL42-06	180.1	183.1	0.016		160	0.11	2.8	1880	1490	6	2	0.01	0.01	10.5	3.0	14	0.57
KL42-06	183.1	185.1	0.0086		86	0.1	0.01	540	355	4	2	0.01	0.01	4.2	1.0	12	0.23
KL42-06	185.1	188.2	0.0037		37	0.09	0.01	140	94	3	2	0.01	0.01	1.2	1.1	13	0.01
KL42-06	188.2	191.3	0.0038		38	0.11	0.5	610	231	10	3	0.01	0.01	2.7	1.1	26	0.21
KL42-06	191.3	193.8	0.003		30	0.09	0.6	271	104	4	3	0.01	0.01	1.8	1.0	26	0.01
KL42-06	193.8	197.4	0.0021		21	0.06	1.2	580	205	8	3	0.01	0.01	3.2	1.5	28	0.01
KL42-06	197.4	200.4	0.0049		49	0.07	4.1	4300	3640	23	4	0.01	0.01	5.3	34.2	18	0.01
KL42-06	200.4	203.1	0.0026		26	0.08	1.5	1630	890	11	2	0.01	0.01	2.4	9.1	17	0.01
KL42-06	203.1	206.2	0.0025		25	0.06	1.1	690	292	9	3	0.01	0.01	1.3	3.5	22	0.01
KL42-06	206.2	209.3	0.0299		299	0.04	0.9	295	128	8	4	0.01	0.01	1	0.9	18	0.01
KL42-06	209.3	212.4	0.004		40	0.03	0.8	230	122	4	2	0.01	0.01	0.8	2.0	20	0.01
KL42-06	212.4	215.4	0.0029		29	0.05	1	520	285	7	2	0.01	0.01	1.2	4.0	24	0.01
KL42-06	215.4	218.4	0.0036		36	0.03	1.1	143	85	2	3	0.01	0.01	0.7	1.6	21	0.01
KL42-06	218.4	221.4	0.0023		23	0.09	1.8	670	280	10	3	0.01	0.01	3.5	2.3	23	0.01
KL42-06	221.4	224.4	0.0041		41	0.22	4.1	2700	890	19	3	0.01	3	11.3	5.5	32	0.3
KL42-06	224.4	227.4	0.0087		87	0.2	5.2	3100	1450	20	2	0.01	4	12.3	5.5	31	0.33
KL42-06	227.4	230.4	0.0115		115	0.29	8.1	5180	2300	31	3	1	2	9.6	5.8	32	0.43
KL42-06	230.4	233.4	0.059		590	0.69	56	39000	17800	180	4	10	0.01	58	26.0	48	2.44
KL42-06	233.4	236.4	0.0065		65	0.14	18	15300	5900	23	3	1	0.01	18.3	9.3	21	0.91
KL42-06	236.4	239.4	0.0028		28	0.03	1	318	154	5	2	0.01	0.01	1.7	3.5	23	0.12
KL42-06	239.4	242.4	0.0035		35	0.11	1.8	1080	480	18	5	0.01	0.01	2.7	9.5	21	0.1
KL42-06	242.4	244.9	0.42		4200	0.24	9	179	223	1300	9	33	4	28	7.3	34	0.5
KL42-06	244.9	247.9	12.02		120200	1.26	110	4000	4800	29000	20	650	0.01	310	80.0	220	8.45
KL42-06	247.9	250.9	12.61		126100	1.4	99	14400	14000	9200	16	765	0.01	95	125.0	233	12
KL42-06	250.9	253.9	0.65		6500	0.77	76	69000	107400	1960	11	105	0.01	95	273.0	186	5.82
KL42-06	253.9	256.4	0.34		3400	1.37	132	139000	135000	1100	8	38	0.01	135	131.0	144	8.96
KL42-06	256.4	259.4	0.054		540	0.2	9.1	5800	6800	140	5	3	0.01	11.2	12.7	33	0.64

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL42-06	259.4	262.4	0.0204		204	0.02	0.6	510	430	42	5	2	0.01	2.1	2.5	31	0.12
KL42-06	262.4	265.4	0.0342		342	0.02	0.01	178	128	32	4	1	0.01	1.1	2.5	36	0.01
KL42-06	265.4	268.4	0.0207		207	0.04	0.6	189	167	28	10	2	0.01	2.2	3.4	42	0.1
KL42-06	268.4	270.4	0.22		2200	0.09	3	223	152	75	8	3	0.01	6.4	3.8	67	0.16
KL42-06	270.4	272.5	0.127		1270	0.58	2.1	228	284	40	10	3	3	3.6	5.0	60	0.01
KL42-06	272.5	275.5	0.54		5400	0.37	14.2	3500	6500	200	36	12	6	6.8	30.0	119	0.44
KL42-06	275.5	278.5	0.215		2150	0.62	16.2	6250	11000	48	23	26	3	2.5	52.8	84	0.3
KL42-06	278.5	281.5	0.63		6300	0.49	10.8	1260	580	120	31	5	4	1.5	15.0	117	0.68
KL42-06	281.5	284.5	0.62		6200	0.77	30.3	13000	22100	160	28	5	4	24	19.5	61	1.42
KL42-06	284.5	287.7	0.82		8200	1.17	2	1080	252	130	16	0.01	6	5.2	15.5	53	0.17
KL42-06	287.7	290.7	0.5		5000	0.84	1.5	289	162	26	5	1	11	2	5.3	41	0.01
KL42-06	290.7	293.7	0.3		3000	0.39	2.7	353	180	290	41	4	4	19.7	7.5	117	0.11
KL42-06	293.7	296.7	0.146		1460	0.16	2	1120	460	180	31	1	3	22	8.3	126	0.14
KL42-06	296.7	299.7	0.0338		338	0.05	0.8	385	138	65	27	2	2	6	2.3	61	0.01
KL42-06	299.7	301.8	0.164		1640	0.14	2	740	295	530	35	2	0.01	30	8.5	91	0.14
KL42-06	301.8	304.8	1.44		14400	1.44	31.8	4200	4300	1020	153	52	12	76	75.5	200	0.62
KL42-06	304.8	307.8	0.74		7400	1.62	22.3	570	422	720	6	32	5	90	13.8	141	0.34
KL42-06	307.8	310.8	1.38		13800	0.92	19.8	211	267	1760	12	75	25	416	41.0	179	0.72
KL42-06	310.8	313.8	0.98		9800	0.36	13.4	85	135	1500	50	155	5	98	11.3	268	0.4
KL42-06	313.8	316.8	0.6		6000	0.41	3.3	167	224	740	122	9	9	64	14.8	292	0.13
KL42-06	316.8	319.8	0.65		6500	0.61	16.9	10600	14700	380	298	4	6	56	19.7	278	1
KL42-06	319.8	322.8	0.252		2520	0.36	1.6	116	134	130	133	3	5	26	9.3	252	0.01
KL42-06	322.8	325.8	0.38		3800	0.34	2.1	172	172	260	278	13	5	66	13.3	145	0.12
KL42-06	325.8	328.8	0.123		1230	0.24	0.8	209	129	88	179	2	7	20	7.3	126	0.01
KL42-06	328.8	331.8	0.845		8450	0.43	4.3	960	192	180	153	7	3	60	8.5	218	0.15
KL42-06	331.8	334.8	0.39		3900	0.26	2.4	810	137	110	96	6	0.01	30	5.5	227	0.13
KL42-06	334.8	337.8	0.201		2010	0.34	1.9	369	109	81	101	7	3	22	5.3	301	0.12
KL42-06	337.8	340.8	2.04		20400	0.43	5.7	430	144	89	150	4	5	26	12.0	361	0.15
KL42-06	340.8	343.8	0.36		3600	0.42	4.1	307	155	360	221	5	6	54	12.0	192	0.01
KL42-06	343.8	346.8	1.02		10200	0.46	5.8	241	147	1200	279	6	4	205	12.0	230	0.12
KL42-06	346.8	349.8	0.223		2230	0.29	1.4	186	76	120	230	3	4	30	5.6	316	0.1
KL42-06	349.8	352.8	0.82		8200	0.28	1.7	149	59	250	191	3	3	38	6.1	192	0.01
KL42-06	352.8	355.8	0.25		2500	0.44	2.1	640	128	220	178	3	4	44	12.5	284	0.1
KL42-06	355.8	358.8	0.193		1930	0.38	2.4	398	770	200	249	4	6	32	12.5	176	0.13
KL42-06	358.8	361.8	0.27		2700	0.94	2.3	280	228	280	328	5	11	52	19.2	287	0.12
KL42-06	361.8	364.8	0.25		2500	0.88	2.2	750	204	72	365	5	13	26	17.3	223	0.16
KL42-06	364.8	367.8	0.41		4100	0.81	2	194	102	73	645	5	28	14.1	13.4	251	0.12
KL42-06	367.8	370.8	0.214		2140	0.39	2.6	780	640	68	252	4	12	10.1	7.3	194	0.11
KL42-06	370.8	373.8	0.056		560	0.26	2.7	372	355	20	6	9	19	2.6	12.5	27	0.01
KL42-06	373.8	376.8	0.151		1510	0.33	1.6	84	230	26	25	6	16	3.7	8.5	73	0.01
KL42-06	376.8	379.8	0.159		1590	0.6	2.2	95	520	37	21	6	18	12.1	11.8	51	0.01
KL42-06	379.8	382.8	0.094		940	0.4	2.7	58	63	33	12	26	17	4.8	16.5	43	0.01
KL42-06	382.8	385.8	0.0179		179	0.54	3	203	76	13	8	2	20	3.2	8.8	21	0.01
KL42-06	385.8	388.8	0.0195		195	0.25	1.9	381	199	17	9	0.01	20	2.4	8.0	20	0.01
KL42-06	388.8	389.4	0.0122		122	0.12	1.4	117	92	11	10	0.01	19	1.7	3.4	35	0.01
KL42-06	389.4	391.8	0.0259		259	0.08	1.1	81	35	13	9	0.01	19	1.6	2.0	42	0.01
KL42-06	391.8	394.8	0.0138		138	0.02	0.01	69	18	14	6	0.01	27	1.2	1.6	34	0.01
KL42-06	394.8	397.8	0.0129		129	0.02	0.5	141	27	18	6	0.01	26	1.5	0.7	33	0.01
KL42-06	397.8	400.8	0.027		270	0.06	0.8	107	62	29	10	0.01	26	1.8	1.3	33	0.01
KL42-06	400.8	403.8	0.0168		168	0.06	0.01	84	23	10	2	0.01	20	1.4	0.9	34	0.01
KL42-06	403.8	406.8	0.509		5090	0.48	22.3	5800	2940	200	50	5	20	29	5.5	93	0.61
KL42-06	406.8	408.1	1.1		11000	0.76	29.5	2900	1680	320	82	28	19	29	34.0	278	0.31
KL42-06	408.1	409.8	1.13		11300	0.6	22.8	1930	1590	92	111	37	14	18.8	21.5	180	0.22
KL42-06	409.8	412.8	0.75		7500	0.53	13.4	5500	1830	71	29	7	10	12.5	9.3	96	0.29
KL42-06	412.8	415.8	3.29		32900	1.84	54	1760	1360	280	31	73	31	70	35.0	139	0.47
KL42-06	415.8	418.8	0.37		3700	0.16	3.6	950	201	32	18	2	4	10.1	8.8	12	0.01
KL42-06	418.8	420.6	1.24		12400	0.49	7.7	3300	1350	48	13	5	16	16.2	12.0	16	0.2
KL42-06	420.6	423.6	1.01		10100	0.21	6.6	3100	330	19	13	15	46	7.2	9.3	21	0.13
KL42-06	423.6	426.6	2.04		20400	0.64	5.5	10100	1150	150	60	14	32	12.7	14.0	28	0.31
KL42-06	426.6	429.6	1.37		13700	1.3	4	32700	45800	72	16	11	12	33	12.0	59	0.44
KL42-06	429.6	432.6	2.22		22200	0.92	4.9	10000	8700	58	47	9	13	19.5	15.0	48	0.18
KL42-06	432.6	435.6	1.28		12800	0.8	6.4	5400	11100	43	15	4	19	20	7.0	36	0.32
KL42-06	435.6	438.6	0.73		7300	0.44	5.2	3200	1030	45	14	24	14	14	5.0	27	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL42-06	438.6	441.6	1.2	12000	0.99	6.1	1310	1950	37	14	16	13	16	13.3	39	0.01
KL42-06	441.6	444.6	1.43	14300	1.22	11.2	3200	350	74	17	5	12	16.8	10.5	31	0.01
KL42-06	444.6	447.6	2.05	20500	1.36	5.1	1710	690	22	24	7	14	19.5	22.0	35	0.01
KL42-06	447.6	450.6	1.28	12800	0.6	4.7	770	1160	21	154	6	11	13.5	12.0	31	0.01
KL42-06	450.6	453.6	1.9	19000	0.36	3.4	282	201	4	33	3	17	3.7	10.5	36	0.01
KL42-06	453.6	456.6	3.44	34400	0.28	3.8	247	49	1	94	5	46	3.4	14.0	26	0.01
KL42-06	456.6	459.6	2.69	26900	0.44	6.3	620	670	7	61	31	32	4	12.0	21	0.01
KL42-06	459.6	462.6	1.27	12700	0.22	1.4	189	41	2	41	6	34	2.7	5.5	27	0.01
KL42-06	462.6	465.6	3.7	37000	1.22	3.6	246	35	1	15	6	33	0.8	8.0	18	0.01
KL42-06	465.6	468.6	1.01	10100	0.41	1.3	362	12	10	87	2	15	0.7	7.5	52	0.01
KL42-06	468.6	471.6	0.42	4200	0.2	0.8	131	37	5	111	0.01	6	2.2	4.3	100	0.01
KL42-06	471.6	474.6	0.223	2230	0.1	0.7	52	28	3	165	0.01	3	2.7	3.5	44	0.01
KL42-06	474.6	477.6	0.193	1930	0.08	0.01	47	9	2	35	0.01	2	0.3	0.9	44	0.01
KL42-06	477.6	480.6	0.085	850	0.06	0.01	48	10	1	70	0.01	3	0.2	1.5	11	0.01
KL42-06	480.6	483.6	0.13	1300	0.07	0.01	54	14	2	84	0.01	0.01	0.3	0.8	19	0.01
KL42-06	483.6	485.5	0.139	1390	0.13	0.01	60	30	2	63	0.01	4	0.3	1.7	53	0.01
KL42-06	485.5	487.6	1.9	19000	1.41	2.1	105	18	5	21	0.01	35	1.1	10.5	44	0.01
KL42-06	487.6	490.6	1.84	18400	0.85	2	150	14	3	10	0.01	39	1.9	14.5	31	0.01
KL42-06	490.6	493.6	1.18	11800	0.74	1.4	135	115	1	18	0.01	18	0.7	8.0	42	0.01
KL42-06	493.6	495.9	0.89	8900	0.46	1	58	38	6	41	0.01	13	0.5	6.0	32	0.01
KL42-06	495.9	497.9	1.05	10500	0.53	2.1	144	92	380	81	12	18	60	11.5	40	0.12
KL42-06	497.9	500.4	0.33	3300	0.16	0.01	147	48	37	39	2	7	3.7	5.0	31	0.01
KL42-06	500.4	502.9	0.224	2240	0.17	0.01	316	145	10	180	0.01	9	1	3.5	66	0.01
KL42-06	502.9	505.9	1.93	19300	1.15	1.9	2890	49	6	254	1	87	1	15.5	82	0.01
KL42-06	505.9	508.9	1.14	11400	0.69	1.1	162	26	2	6	1	46	0.5	13.5	62	0.01
KL42-06	508.9	511.9	2.34	23400	1.51	7.1	124	97	7	12	6	45	7.8	25.5	88	0.71
KL42-06	511.9	514.9	0.528	5280	0.25	0.7	43	9	0.01	7	0.01	24	1	3.3	28	0.01
KL42-06	514.9	515.5	0.335	3350	0.12	0.01	67	33	1	15	0.01	22	0.01	2.8	54	0.01
KL42-06	515.5	518.5	0.2	2000	0.07	0.01	32	19	28	45	1	6	2.1	2.8	91	0.01
KL42-06	518.5	521.5	0.151	1510	0.08	1.2	30	25	18	145	4	3	12.5	3.5	119	0.01
KL42-06	521.5	524.5	0.162	1620	0.09	1.4	26	14	26	87	2	5	7.3	5.1	145	0.01
KL42-06	524.5	527.5	0.107	1070	0.08	0.8	25	9	66	47	1	4	11.5	3.8	58	0.01
KL42-06	527.5	530.5	0.0317	317	0.07	0.01	19	9	29	34	1	6	3.5	3.9	127	0.01
KL42-06	530.5	533.5	0.078	780	0.08	1.1	22	35	34	68	3	6	4.4	3.5	85	0.01
KL42-06	533.5	536.5	0.0134	134	0.03	0.01	17	11	7	64	0.01	5	0.6	3.9	61	0.01
KL42-06	536.5	539.5	0.0255	255	0.04	0.01	14	7	20	68	0.01	5	2	2.5	141	0.01
KL42-06	539.5	542.5	0.084	840	0.05	0.01	13	8	33	72	0.01	4	3.3	1.8	181	0.01
KL42-06	542.5	545.5	0.0289	289	0.03	0.01	64	60	26	36	1	2	2.8	2.0	151	0.01
KL42-06	545.5	548.5	0.0214	214	0.03	0.01	17	13	13	52	0.01	3	2.3	2.1	204	0.01
KL42-06	548.5	551.5	0.076	760	0.03	0.01	14	13	12	40	0.01	2	2.4	2.5	67	0.01
KL42-06	551.5	554.5	0.037	370	0.02	0.01	16	9	12	62	0.01	4	0.9	2.0	209	0.01
KL42-06	554.5	557.5	0.045	450	0.03	0.01	23	12	8	51	1	3	1.1	2.4	236	0.01
KL42-06	557.5	560.5	0.051	510	0.03	0.01	11	8	14	160	0.01	2	1.4	1.2	179	0.01
KL42-06	560.5	563.5	0.073	730	0.03	0.01	12	14	11	231	0.01	4	1.3	1.9	57	0.01
KL42-06	563.5	566.5	0.0284	284	0.02	0.01	15	9	7	72	0.01	5	1.2	2.9	158	0.01
KL42-06	566.5	569.5	0.0354	354	0.04	0.01	21	10	19	52	0.01	3	1.4	2.5	137	0.01
KL42-06	569.5	572.5	0.048	480	0.03	0.01	17	9	20	98	0.01	8	1.9	1.9	160	0.01
KL42-06	572.5	575.5	0.0262	262	0.02	0.01	14	10	12	63	0.01	5	1	2.3	235	0.01
KL42-06	575.5	578.5	0.048	480	0.03	0.01	35	14	9	106	0.01	8	1.4	2.1	67	0.01
KL42-06	578.5	581.5	0.0341	341	0.03	0.01	8	8	7	136	0.01	4	1.1	1.6	50	0.01
KL42-06	581.5	584.5	0.022	220	0.01	0.01	35	252	7	56	0.01	8	0.9	2.0	34	0.01
KL42-06	584.5	587.5	0.0084	84	0.02	0.01	17	14	2	114	0.01	6	0.3	1.1	242	0.01
KL42-06	587.5	590.5	0.0158	158	0.02	0.01	273	128	27	81	0.01	10	1.5	3.6	167	0.01
KL42-06	590.5	593.5	0.0151	151	0.02	0.01	26	13	28	79	0.01	3	3.1	1.2	198	0.01
KL42-06	593.5	596.5	0.076	760	0.03	0.01	14	14	47	133	0.01	2	5.3	1.6	56	0.01
KL42-06	596.5	599.6	0.054	540	0.03	0.01	15	11	53	109	0.01	3	3.5	0.8	51	0.01
KL42-06	599.6	602.7	0.0191	191	0.01	0.01	20	19	8	36	0.01	6	0.5	2.8	26	0.01
KL42-06	602.7	605.9	0.0202	202	0.01	0.01	15	9	7	13	0.01	4	0.5	1.7	35	0.01
KL42-06	605.9	609	0.062	620	0.05	0.01	22	11	32	450	0.01	3	2.2	2.2	231	0.01
KL42-06	609	612	0.0229	229	0.01	0.01	20	9	14	231	0.01	0.01	1.2	1.2	30	0.01
KL42-06	612	615	0.167	1670	0.03	0.9	52	32	120	34	1	3	8.6	2.0	205	0.01
KL42-06	615	618.2	0.66	6600	0.07	3.1	162	365	2200	34	2	6	207	2.5	252	0.1
KL42-06	618.2	621.5	0.2	2000	0.06	1.4	33	40	620	47	2	3	46	4.0	210	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL42-06	621.5	624.3	0.119		1190	0.03	2	36	25	290	76	2	0.01	26	2.1	226	0.01
KL42-06	624.3	627.3	0.202		2020	0.04	1.7	126	93	230	42	2	0.01	19.5	1.9	236	0.01
KL42-06	627.3	630.3	0.144		1440	0.07	1.1	110	61	5	27	1	0.01	1.3	1.4	29	0.01
KL42-06	630.3	633.3	0.0281		281	0.01	0.01	53	33	4	65	1	0.01	0.3	1.8	23	0.01
KL42-06	633.3	636.3	0.079		790	0.02	0.6	147	56	16	42	1	2	1.8	2.0	245	0.01
KL42-06	636.3	639.3	0.054		540	0.01	0.01	75	48	17	23	1	4	1.2	2.3	12	0.01
KL42-06	639.3	642.3	0.089		890	0.01	0.9	66	36	10	35	2	3	2.1	1.2	10	0.01
KL42-06	642.3	645.3	0.131		1310	0.01	0.9	181	92	55	44	2	3	3	1.9	229	0.01
KL42-06	645.3	648.3	0.088		880	0.03	0.01	114	33	110	79	2	0.01	6.8	2.5	15	0.01
KL42-06	648.3	651.3	0.054		540	0.05	0.01	168	51	27	117	1	3	3.1	7.9	10	0.01
KL42-06	651.3	654.3	0.031		310	0.01	0.01	104	25	15	40	1	6	1.5	5.0	14	0.01
KL42-06	654.3	656.7	0.126		1260	0.02	0.01	71	29	24	101	2	0.01	0.8	1.8	8	0.01
KL42-06	656.7	659.7	0.018		180	0.01	0.01	26	10	15	106	0.01	0.01	1	1.5	24	0.01
KL42-06	659.7	662.7	0.0266		266	0.05	0.01	45	12	31	28	1	5	2.5	8.8	27	0.01
KL42-06	662.7	665.7	0.0319		319	0.02	0.01	27	12	44	50	0.01	2	1.9	0.5	174	0.01
KL42-06	665.7	668.7	0.0127		127	0.02	0.01	42	19	18	236	0.01	3	1.2	1.4	284	0.01
KL42-06	668.7	671.7	0.0243		243	0.01	0.01	69	21	7	73	0.01	3	0.6	1.0	260	0.01
KL42-06	671.7	674.7	0.073		730	0.04	0.01	50	13	8	55	2	0.01	1	4.3	177	0.01
KL42-06	674.7	677.7	0.0203		203	0.02	0.01	130	12	8	192	0.01	0.01	0.4	2.0	140	0.01
KL42-06	677.7	680.7	0.0145		145	0.02	0.01	80	14	7	37	0.01	0.01	0.5	1.8	160	0.01
KL42-06	680.7	683.7	0.0301		301	0.02	0.01	185	11	10	37	0.01	0.01	0.7	1.3	247	0.01
KL42-06	683.7	686.7	0.073		730	0.02	0.01	19	14	4	47	1	2	0.5	1.8	139	0.01
KL42-06	686.7	689.7	0.083		830	0.03	0.01	57	35	19	25	1	0.01	0.5	1.5	192	0.01
KL42-06	689.7	692.7	0.066		660	0.04	0.8	208	76	29	20	1	0.01	0.9	2.0	126	0.01
KL42-06	692.7	695.7	0.088		880	0.04	0.01	117	59	160	62	1	4	1.9	1.8	124	0.01
KL42-06	695.7	698.7	0.0225		225	0.06	0.01	209	86	39	78	1	5	1.5	3.3	207	0.01
KL42-06	698.7	701.7	0.165		1650	0.04	1	420	178	76	56	1	2	1	2.5	174	0.01
KL42-06	701.7	704.7	0.102		1020	0.03	0.9	48	37	160	40	1	4	0.9	1.8	117	0.01
KL42-06	704.7	707.7	0.057		570	0.04	0.01	125	45	100	61	1	6	2.2	3.0	152	0.01
KL42-06	707.7	710.7	0.13		1300	0.05	0.6	80	31	56	54	1	3	1.7	2.9	118	0.01
KL42-06	710.7	713.7	0.276		2760	0.11	1.1	177	47	650	45	2	4	12.5	2.0	166	0.01
KL42-06	713.7	716.7	0.21		2100	0.08	1.1	224	111	240	23	2	8	10.4	9.3	155	0.01
KL42-06	716.7	719.7	0.175		1750	0.03	0.9	51	31	18	30	1	2	0.8	1.7	123	0.01
KL42-06	719.7	722.7	0.113		1130	0.01	0.01	34	19	3	27	0.01	0.01	0.2	2.0	178	0.01
KL42-06	722.7	725.7	0.151		1510	0.03	1.1	98	41	80	47	1	2	2.3	2.4	143	0.01
KL42-06	725.7	728.7	0.176		1760	0.02	1	78	31	69	26	1	0.01	2.5	2.5	99	0.01
KL42-06	728.7	731.7	0.121		1210	0.02	0.7	66	24	15	28	1	0.01	0.8	1.4	99	0.01
KL42-06	731.7	734.7	0.138		1380	0.02	0.7	38	15	9	61	1	0.01	0.3	3.0	109	0.01
KL42-06	734.7	737.7	0.264		2640	0.06	1	54	44	47	79	1	0.01	1.8	1.9	90	0.01
KL42-06	737.7	740.7	0.091		910	0.03	0.01	24	11	5	32	1	3	0.3	2.3	193	0.01
KL42-06	740.7	743.7	0.118		1180	0.02	0.01	21	15	5	32	2	2	0.6	3.2	86	0.01
KL42-06	743.7	746.7	0.171		1710	0.04	0.8	19	10	2	15	1	2	0.2	2.0	144	0.01
KL42-06	746.7	749.7	0.108		1080	0.04	0.01	210	62	3	23	1	0.01	0.5	2.0	125	0.01
KL42-06	749.7	752.7	0.119		1190	0.02	0.01	78	66	27	17	1	0.01	0.4	1.9	161	0.01
KL42-06	752.7	755.7	0.2		2000	0.04	1	61	28	3	15	1	0.01	0.7	2.8	119	0.01
KL42-06	755.7	758.7	0.427		4270	0.06	1.1	22	22	120	20	2	0.01	0.3	1.6	98	0.01
KL42-06	758.7	761.7	0.062		620	0.02	0.01	39	23	17	12	0.01	0.01	0.9	1.6	106	0.01
KL42-06	761.7	764.7	0.101		1010	0.02	0.01	40	20	2	14	0.01	0.01	0.2	1.0	203	0.01
KL42-06	764.7	767.7	0.103		1030	0.02	0.6	43	30	3	11	1	0.01	0.3	1.8	134	0.01
KL42-06	767.7	770.7	0.095		950	0.01	0.7	42	20	4	6	0.01	0.01	0.2	1.6	177	0.01
KL42-06	770.7	774.3	0.124		1240	0.03	0.8	119	42	150	35	1	0.01	9.3	2.1	147	0.01
KL42-07	0	2.6	0.0087		87	0.02	0.01	197	138	20	56	0.01	0.01	5.1	1.5	29	0.01
KL42-07	2.6	5.6	0.0084		84	0.01	0.01	146	79	11	7	0.01	0.01	4	1.2	13	0.01
KL42-07	5.6	8.6	0.0138		138	0.05	0.7	231	98	22	8	0.01	0.01	2.9	1.9	14	0.01
KL42-07	8.6	10.9	0.0094		94	0.02	0.9	520	139	35	23	2	0.01	3.4	1.4	16	0.01
KL42-07	10.9	14	0.0024		24	0.04	0.8	203	63	21	10	0.01	0.01	3.6	2.1	16	0.01
KL42-07	14	17.1	0.0009		9	0.09	0.6	77	48	9	4	0.01	0.01	1.5	1.5	15	0.11
KL42-07	17.1	20.2	0.0023		23	0.02	0.7	60	52	11	3	0.01	2	1.2	1.2	23	0.01
KL42-07	20.2	23.3	0.0331		331	0.04	1.1	330	149	88	43	3	0.01	12	2.4	30	0.16
KL42-07	23.3	26.4	0.012		120	0.01	0.01	36	27	10	4	0.01	3	1.1	0.9	40	0.01
KL42-07	26.4	29.5	0.0034		34	0.04	0.6	89	72	14	3	0.01	0.01	2	1.2	21	0.01
KL42-07	29.5	32.6	0.0128		128	0.04	0.9	122	68	11	2	0.01	2	1.8	0.8	42	0.14
KL42-07	32.6	35.6	0.0076		76	0.02	1	85	61	15	3	0.01	0.01	1.9	1.5	32	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL42-07	35.6	38.6	0.006		60	0.01	0.7	85	63	18	8	0.01	2	2.5	2.4	24	0.01
KL42-07	38.6	41.6	0.0034		34	0.01	0.6	96	68	14	10	0.01	3	2	2.6	22	0.01
KL42-07	41.6	44.6	0.0208		208	0.01	1.3	285	143	31	104	2	2	3.2	3.1	37	0.01
KL42-07	44.6	47.6	0.0123		123	0.02	2.5	283	670	34	34	0.01	0.01	5.2	6.3	23	0.12
KL42-07	47.6	50.6	0.002		20	0.01	0.7	42	54	7	0.01	0.01	0.01	2.1	0.9	19	0.01
KL42-07	50.6	53.6	0.0053		53	0.01	0.01	46	54	6	0.01	0.01	0.01	1	1.0	26	0.01
KL42-07	53.6	56.6	0.0034		34	0.02	0.01	79	37	2	3	0.01	2	1.2	1.9	19	0.01
KL42-07	56.6	57.6	0.0074		74	0.03	0.01	53	27	7	4	0.01	0.01	1.1	2.3	23	0.01
KL42-07	57.6	59.6	0.0025		25	0.03	0.01	48	25	10	12	0.01	0.01	0.7	1.5	21	0.01
KL42-07	59.6	62.6	0.0016		16	0.1	0.01	45	34	19	114	0.01	0.01	1.3	1.9	32	0.01
KL42-07	62.6	65.6	0.0117		117	0.07	0.01	91	56	17	10	0.01	0.01	2.1	2.0	20	0.01
KL42-07	65.6	68.6	0.003		30	0.03	0.01	65	39	13	4	0.01	0.01	1.2	2.4	29	0.01
KL42-07	68.6	71.6	0.0109		109	0.06	2.4	265	450	69	9	5	3	2.6	5.9	29	0.01
KL42-07	71.6	74.6	0.0195		195	0.03	0.6	124	73	23	9	2	2	2	2.4	24	0.12
KL42-07	74.6	77.6	0.005		50	0.03	0.01	250	86	38	10	0.01	0.01	8.7	1.7	24	0.01
KL42-07	77.6	80.6	0.033		330	0.05	0.5	174	107	58	23	1	0.01	2.3	3.7	34	0.01
KL42-07	80.6	83.6	0.052		520	0.2	3.7	4610	2980	120	11	11	5	4.2	20.8	51	0.01
KL42-07	83.6	86.6	0.0245		245	0.04	0.7	460	206	42	30	0.01	0.01	1.8	2.5	22	0.01
KL42-07	86.6	89.6	0.0108		108	0.04	1	470	214	71	28	4	2	6.1	4.4	29	0.01
KL42-07	89.6	92.6	0.07		700	0.12	0.9	630	244	80	167	3	4	6.5	4.4	56	0.01
KL42-07	92.6	94.3	0.0161		161	0.05	0.01	120	36	43	55	0.01	0.01	3.9	1.3	51	0.01
KL42-07	94.3	96.5	0.0167		167	0.02	0.01	190	64	32	220	3	3	2	1.6	36	0.01
KL42-07	96.5	98.6	0.0266		266	0.05	0.01	580	96	51	210	1	4	4.1	2.0	65	0.01
KL42-07	98.6	101.6	0.042		420	0.06	1.9	3380	331	100	103	17	2	3.4	4.5	40	0.01
KL42-07	101.6	103	0.058		580	0.1	2.1	860	430	94	420	5	3	4.9	5.7	74	0.1
KL42-07	103	104.6	0.0425		425	0.08	1.6	950	401	83	397	6	4	2.6	3.4	25	0.01
KL42-07	104.6	107.6	0.006		60	0.03	0.8	430	180	60	620	5	0.01	2.2	2.5	28	0.01
KL42-07	107.6	110.6	0.006		60	0.47	1.4	560	383	200	3700	24	3	12	13.5	99	0.15
KL42-07	110.6	113.6	0.0186		186	0.19	1.3	1180	261	200	890	5	0.01	3.9	3.7	88	0.01
KL42-07	113.6	116.6	0.0053		53	0.39	3.4	418	302	280	750	24	0.01	7.1	7.8	51	0.01
KL42-07	116.6	119.6	0.071		710	0.31	10.5	1220	880	230	1530	72	6	7.4	6.8	45	0.1
KL42-07	119.6	122.6	0.0209		209	0.39	10.6	1160	1310	290	1920	42	3	9.6	9.3	38	0.1
KL42-07	122.6	125.6	0.045		450	0.44	6.1	2970	1860	370	700	28	8	7.5	11.2	25	0.25
KL42-07	125.6	128.3	0.103		1030	0.35	5.5	3400	1280	320	398	56	9	8.8	8.5	39	0.12
KL42-07	128.3	131	0.262		2620	0.25	4.2	4230	580	310	95	13	11	13	6.8	35	0.21
KL42-07	131	133.5	0.339		3390	0.37	7.2	3820	1310	1240	419	36	11	115	13.0	30	1.26
KL42-07	133.5	135	0.6		6000	0.39	10.8	6010	2060	2400	765	95	24	42	10.5	38	0.61
KL42-07	135	137.7	0.0145		145	0.05	1.6	2740	890	62	55	1	3	2.2	3.4	19	0.19
KL42-07	137.7	140.6	0.0124		124	0.04	0.7	810	269	31	45	4	0.01	1.8	2.0	23	0.01
KL42-07	140.6	143.6	0.0145		145	0.09	1.2	1430	810	41	65	3	0.01	1.6	3.8	26	0.01
KL42-07	143.6	145.8	0.0152		152	0.04	0.6	1300	580	38	42	2	0.01	3.1	2.0	23	0.01
KL42-07	145.8	148.5	0.0265		265	0.07	1.2	900	359	41	27	4	0.01	1.2	3.3	26	0.01
KL42-07	148.5	150.1	0.169		1690	0.21	8.7	14800	1450	550	225	68	7	15.5	18.3	34	0.23
KL42-07	150.1	152.9	0.028		280	0.05	1.3	1100	440	63	79	4	2	0.4	3.3	26	0.01
KL42-07	152.9	155.9	0.111		1110	0.13	1.6	800	262	40	140	6	4	1.3	2.5	44	0.01
KL42-07	155.9	158.6	0.42		4200	0.89	28	24900	6700	670	363	58	22	7.4	37.0	131	0.01
KL42-07	158.6	160	0.69		6900	0.45	13.6	17700	3500	1900	367	26	22	12.9	18.0	34	0.1
KL42-07	160	163	0.56		5600	0.47	9	36900	4000	970	393	21	28	12.3	23.0	32	0.1
KL42-07	163	166	1.5		15000	1.46	16.9	41300	4500	3800	170	21	70	19.6	35.5	29	0.01
KL42-07	166	169.1	4.32		43200	2.06	63	84700	11700	6300	215	35	147	29.8	72.5	53	0.01
KL42-07	169.1	170.8	1.82		18200	1.6	23	57000	940	1670	2015	105	98	4.5	97.0	88	0.01
KL42-07	170.8	173.6	1.08		10800	1.16	5.6	2800	460	850	452	33	26	6.5	40.0	44	0.01
KL42-07	173.6	176.6	0.376		3760	0.69	7	3470	2280	110	7235	22	28	6	25.0	32	0.01
KL42-07	176.6	179.6	1.29		12900	1.3	10.8	39500	480	200	2280	31	65	10.8	35.0	66	0.01
KL42-07	179.6	182.4	0.86		8600	1.08	5.3	3000	510	120	784	27	27	5.5	32.0	54	0.11
KL42-07	182.4	183.4	1.62		16200	0.98	18.1	30200	1620	160	165	19	33	5.5	40.0	63	0.16
KL42-07	183.4	188.5	1.3		13000	0.92	12.5	56000	550	130	176	31	78	6.3	55.0	58	0.01
KL42-07	188.5	191.6	1.22		12200	1.18	8.9	8900	184	220	147	21	132	8.5	27.0	62	0.4
KL42-07	191.6	193.4	1.2		12000	1.4	14.5	3500	2100	210	61	23	36	7.8	35.0	97	1.62
KL42-07	193.4	194.6	4.24		42400	0.72	8.4	420	108	130	179	21	54	3.7	47.5	81	0.2
KL42-07	194.6	197.6	0.259		2590	0.28	1.2	470	108	61	159	12	37	3.3	34.0	103	0.01
KL42-07	197.6	200.6	0.458		4580	0.41	4.7	650	690	43	378	7	32	4	46.0	44	0.01
KL42-07	200.6	203.6	0.482		4820	0.64	3.6	460	266	73	723	16	33	2	34.0	35	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL42-07	203.6	206.6	0.67	6700	0.44	5.4	1290	1010	70	461	12	29	3.5	33.0	74	0.01
KL42-07	206.6	209.1	0.99	9900	0.84	26	3600	3500	120	642	28	16	3.8	31.0	125	0.12
KL42-07	209.1	212.2	1.31	13100	0.68	17.5	3500	2800	130	496	41	9	2.3	13.5	211	0.17
KL42-07	212.2	214.3	2.18	21800	1.78	49	14500	9200	150	448	70	22	6.5	29.0	70	0.97
KL42-07	214.3	217.4	1.27	12700	1.3	74	48000	51900	210	212	218	18	16.4	47.0	162	5.96
KL42-07	217.4	218.6	0.81	8100	0.52	16.9	1450	1120	62	251	20	15	4.5	35.0	167	0.2
KL42-07	218.6	221.6	1.57	15700	1.2	22.5	910	1140	72	235	34	39	6	25.0	76	0.2
KL42-07	221.6	224.6	3.04	30400	1.38	72	2900	14200	240	333	42	38	20.7	37.5	95	0.19
KL42-07	224.6	227.6	1.74	17400	2.06	86	6000	19200	510	376	113	23	23.3	35.0	114	0.13
KL42-07	227.6	230.4	2.21	22100	1.95	55	2070	3800	420	147	48	37	12.3	24.0	84	0.01
KL42-07	230.4	233.5	4.49	44900	1.98	101	8100	14500	240	94	40	51	23.1	32.5	101	0.01
KL42-07	233.5	236.6	3.86	38600	1.92	42	1190	640	370	244	24	57	9.5	40.0	71	0.01
KL42-07	236.6	239	2.52	25200	1.58	33.8	1950	2700	550	201	40	26	9.3	23.0	61	0.15
KL42-07	239	241	1.24	12400	1.07	19.5	1180	1120	300	87	28	18	8	17.0	61	0.12
KL42-07	241	242.6	1.11	11100	1.01	23.6	2500	3200	460	327	38	22	9.8	23.0	69	0.14
KL42-07	242.6	245.6	2.18	21800	1.11	28	2700	3100	820	818	18	26	9.7	22.0	83	0.2
KL42-07	245.6	248.6	1.85	18500	1.6	21.2	780	590	1340	219	22	43	10.6	23.0	125	0.15
KL42-07	248.6	250.8	1.16	11600	1.75	20.2	212	230	1590	36	20	44	11.7	19.0	91	0.01
KL42-07	250.8	253.1	1.32	13200	1.45	26.8	1400	770	2460	95	38	36	13	25.0	59	0.12
KL42-07	253.1	254.6	2.25	22500	2.4	44	2600	5300	1560	234	32	27	18.5	22.5	126	0.01
KL42-07	254.6	257.6	2.16	21600	2.48	39.6	3100	2400	730	222	32	34	9.2	32.0	150	0.01
KL42-07	257.6	260.2	1.74	17400	2.61	23.1	660	410	400	62	34	29	25	31.0	58	0.01
KL42-07	260.2	263	2.34	23400	2.08	26.6	1280	830	310	184	18	59	18.5	31.0	70	0.01
KL42-07	263	266.1	2.93	29300	1.82	23.7	1450	1150	340	306	6	67	5.5	37.0	116	0.01
KL42-07	266.1	268.7	2.24	22400	2.67	26.9	5100	1010	700	156	22	51	6.6	30.0	50	0.17
KL42-07	268.7	271.8	2.8	28000	2.64	24.6	2400	1560	470	210	24	41	6.4	24.0	54	0.22
KL42-07	271.8	274.9	1.99	19900	4.61	20.9	5700	2900	370	154	24	90	6.3	53.5	76	0.23
KL42-07	274.9	278.2	1.12	11200	2.16	7	1330	520	190	339	16	46	7.1	59.0	59	0.12
KL42-07	278.2	281.3	3.45	34500	2.99	10.6	219	139	89	119	24	28	2.8	38.8	86	0.01
KL42-07	281.3	284.4	1.98	19800	2.53	8	520	340	80	213	20	31	2.3	23.0	107	0.01
KL42-07	284.4	287.5	2.17	21700	2.56	17.9	1060	500	110	110	38	26	2.9	29.0	105	0.01
KL42-07	287.5	290.6	2.4	24000	2.53	20.7	1240	560	120	110	64	20	2.3	17.0	133	0.01
KL42-07	290.6	293.6	2.01	20100	3.41	15.8	1360	1070	120	189	55	19	2.5	24.0	120	0.01
KL42-07	293.6	296.6	1.82	18200	2.36	10.6	1040	500	130	94	11	36	3.1	21.0	124	0.01
KL42-07	296.6	299.6	1.33	13300	2.3	4.7	2800	610	86	452	12	32	8.4	15.0	35	0.01
KL42-07	299.6	302.6	1.32	13200	1.96	3.6	910	321	70	143	9	30	3.5	24.5	92	0.01
KL42-07	302.6	305.6	0.95	9500	2.18	4.7	1870	820	210	68	20	46	8.8	19.5	126	0.01
KL42-07	305.6	308.6	1.7	17000	2.32	6.6	1040	660	210	43	6	64	8.9	23.0	48	0.01
KL42-07	308.6	311.6	0.88	8800	1.48	4.7	1950	990	90	42	9	57	3	80.0	104	0.01
KL42-07	311.6	314.6	0.97	9700	1.56	4.7	1560	730	130	31	7	53	7.2	72.0	112	0.01
KL42-07	314.6	319.6	1.03	10300	1.81	6.6	730	328	240	32	9	56	17.1	33.5	69	0.01
KL42-07	319.6	320.6	1.54	15400	1.95	8.3	281	95	66	28	11	42	4.6	20.0	43	0.01
KL42-07	320.6	323.6	1.29	12900	2.21	5.3	337	191	86	87	6	47	10.3	29.0	38	0.01
KL42-07	323.6	326.6	1.69	16900	2.19	6.7	500	149	64	87	2	65	7	29.5	49	0.01
KL42-07	326.6	329.6	1.19	11900	2.19	8.4	630	164	78	70	7	34	5.5	35.5	45	0.01
KL42-07	329.6	332.6	0.62	6200	2	7.8	750	480	77	92	8	62	6.5	38.5	130	0.01
KL42-07	332.6	335.6	0.45	4500	1.6	7.6	4320	2100	160	132	9	46	9.1	36.0	128	0.01
KL42-07	335.6	338.6	0.38	3800	1.32	4.4	375	200	74	46	10	45	3.2	47.0	52	0.01
KL42-07	338.6	341.6	0.35	3500	1.4	5.6	800	940	130	59	16	26	5.2	36.5	98	0.01
KL42-07	341.6	344.6	0.45	4500	1.24	7	8500	1400	160	108	14	29	4.3	40.5	185	0.01
KL42-07	344.6	347.6	0.4	4000	0.88	3.8	255	240	76	23	18	52	4.1	38.5	120	0.01
KL42-07	347.6	350.6	0.55	5500	0.82	2.9	239	378	88	53	12	29	3	28.5	102	0.01
KL42-07	350.6	353.1	0.465	4650	1.08	2.3	880	328	250	18	20	33	6	20.0	101	0.01
KL42-07	353.1	356.2	0.98	9800	1.28	4.9	4800	790	370	215	22	30	3.3	27.0	95	0.01
KL42-07	356.2	357.8	1.01	10100	1.4	3.3	289	530	47	32	27	11	1.3	38.5	131	0.01
KL42-07	357.8	359.6	0.392	3920	0.54	1.2	124	193	44	66	8	25	0.8	60.5	87	0.01
KL42-07	359.6	362.6	1.39	13900	1.5	4.8	359	230	83	30	54	45	3	27.5	76	0.01
KL42-07	362.6	365.6	1.52	15200	1.94	5.3	410	273	72	33	44	55	3.2	19.5	80	0.01
KL42-07	365.6	368.6	0.68	6800	1.38	2.6	364	233	220	34	40	75	5.4	35.0	111	0.01
KL42-07	368.6	371.6	1.1	11000	2.26	4.7	700	530	230	65	7	88	10.1	26.0	73	0.01
KL42-07	371.6	374.6	1.02	10200	1.82	3.9	1130	430	160	94	8	35	8.4	23.5	131	0.01
KL42-07	374.6	377.6	1.71	17100	2.07	4.8	1270	720	70	151	8	31	12.1	21.5	92	0.01
KL42-07	377.6	380.6	1.29	12900	1.5	4.4	920	430	64	417	8	16	5.2	20.0	73	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL42-07	380.6	383.6	1.53	15300	1.7	5.2	1670	350	34	364	10	34	4.6	20.0	57	0.01
KL42-07	383.6	386.6	1.55	15500	1.76	5.8	1030	369	40	155	7	43	3.9	31.5	131	0.01
KL42-07	386.6	389.6	1.45	14500	1.52	4.6	500	251	33	579	4	25	2.7	20.0	92	0.01
KL42-07	389.6	392.6	1.53	15300	1.34	7	480	201	38	170	6	20	3.1	28.0	111	0.01
KL42-07	392.6	395.6	1.82	18200	1.92	4.7	490	173	10	80	4	27	1.9	18.0	46	0.01
KL42-07	395.6	398.6	1.17	11700	1.51	6	570	265	48	136	34	34	2.2	22.5	98	0.01
KL42-07	398.6	401.6	0.71	7100	1.14	3.1	382	316	94	97	30	40	1.9	27.5	101	0.01
KL42-07	401.6	404.6	1.78	17800	2.21	10	580	345	64	486	10	34	5.4	24.0	103	0.01
KL42-07	404.6	407.6	1.22	12200	2.22	6.5	1020	670	84	174	5	30	7.2	24.5	100	0.01
KL42-07	407.6	410.6	4.41	44100	2.72	18	1050	410	52	349	3	48	4.1	26.0	90	0.01
KL42-07	410.6	411.6	1.03	10300	1.23	8.3	410	281	160	505	3	12	5.4	17.0	61	0.01
KL42-07	411.6	413.6	0.268	2680	0.51	3.2	321	260	59	158	4	14	4	12.5	75	0.01
KL42-07	413.6	416.6	0.16	1600	0.6	2.8	740	334	78	112	36	7	3.3	12.3	47	0.01
KL42-07	416.6	419.3	0.27	2700	0.85	5.5	490	395	68	547	18	7	2.4	13.3	132	0.01
KL42-07	419.3	422.4	0.86	8600	0.55	5.8	216	265	46	3030	22	12	2.9	17.8	128	0.01
KL42-07	422.4	425.5	0.85	8500	0.37	4.2	194	249	230	1640	6	10	16.3	15.4	122	0.01
KL42-07	425.5	428.6	0.45	4500	0.38	3	172	150	120	614	4	5	15	21.5	134	0.01
KL42-07	428.6	431.6	0.34	3400	0.19	2.6	234	105	480	610	3	4	19	7.8	61	0.01
KL42-07	431.6	434.6	0.39	3900	0.17	2.3	148	163	140	540	5	5	5.5	7.3	45	0.01
KL42-07	434.6	436	0.8	8000	0.3	3.1	212	80	170	540	4	7	6.8	7.0	36	0.01
KL42-07	436	437.7	1.2	12000	1.1	13.4	490	365	80	511	49	11	3.5	14.5	56	0.01
KL42-07	437.7	440.1	0.28	2800	0.72	5.9	480	264	83	62	14	10	1.8	9.8	157	0.01
KL42-07	440.1	443.2	0.23	2300	0.9	4.8	740	390	150	644	10	7	2.3	8.8	51	0.01
KL42-07	443.2	446.2	1.12	11200	3.14	9.6	1580	2300	500	930	3	67	6.2	40.0	81	0.01
KL42-07	446.2	448.5	3.32	33200	2.8	13	2800	1620	750	678	1	33	4.3	31.0	85	0.13
KL42-07	448.5	451.5	0.36	3600	2.16	4.4	5200	3100	680	141	19	29	17.1	21.5	56	0.01
KL42-07	451.5	454	0.062	620	0.85	3.2	8800	3700	410	29	62	2	15	6.5	36	0.01
KL42-07	454	455.6	0.2	2000	1.84	6.4	2600	730	400	295	140	3	7.3	8.3	48	0.01
KL42-07	455.6	458.6	0.0127	127	0.07	0.01	107	37	15	12	1	0.01	0.7	2.1	18	0.01
KL42-07	458.6	461.6	0.188	1880	0.49	1.6	710	222	230	71	5	4	8.9	8.3	41	0.01
KL42-07	461.6	464.6	0.207	2070	0.67	4.7	1110	1160	270	111	27	7	14	9.3	26	0.01
KL42-07	464.6	467.6	0.55	5500	0.98	3.8	1000	610	320	350	7	15	13	11.0	43	0.01
KL42-07	467.6	470.6	0.2	2000	0.44	2.2	1350	680	260	145	4	5	11	8.0	51	0.01
KL42-07	470.6	473.6	0.048	480	0.25	3.4	1230	618	120	62	5	0.01	6.7	6.0	21	0.01
KL42-07	473.6	476.6	0.0361	361	0.13	0.8	480	198	49	36	6	0.01	2.2	3.0	20	0.01
KL42-07	476.6	479.6	0.0025	25	0.01	0.01	243	95	5	6	0.01	0.01	0.6	1.8	12	0.01
KL42-07	479.6	482.6	0.009	90	0.03	0.01	67	28	10	10	0.01	0.01	0.5	1.3	15	0.01
KL42-07	482.6	485.6	0.0066	66	0.05	0.01	157	377	19	10	0.01	0.01	1.8	1.8	17	0.01
KL42-07	485.6	488.6	0.0074	74	0.08	0.8	260	530	29	8	0.01	0.01	2.9	1.3	24	0.01
KL42-07	488.6	491.6	0.0022	22	0.01	0.01	31	18	10	4	0.01	0.01	0.5	1.0	11	0.01
KL42-07	491.6	494.6	0.0011	11	0.01	0.01	17	9	9	2	0.01	0.01	0.4	0.9	9	0.01
KL42-07	494.6	497.6	0.0009	9	0.01	0.01	13	6	14	2	0.01	0.01	0.4	1.1	17	0.01
KL42-07	497.6	500.6	0.0007	7	0.06	0.01	55	15	27	3	0.01	2	1.2	1.1	17	0.01
KL42-07	500.6	503.6	0.0029	29	0.06	0.01	79	20	65	4	0.01	0.01	2.1	1.6	25	0.1
KL42-07	503.6	506.6	0.0038	38	0.28	0.01	85	23	53	9	0.01	2	3.8	2.1	20	0.2
KL42-07	506.6	509.6	0.0009	9	0.15	0.01	45	19	32	6	0.01	0.01	2.4	1.4	19	0.1
KL42-07	509.6	512.6	0.0032	32	0.05	0.01	30	8	22	10	0.01	0.01	1.1	0.5	14	0.01
KL42-07	512.6	515.6	0.0038	38	0.04	0.01	39	9	24	8	0.01	0.01	0.7	1.1	13	0.01
KL42-07	515.6	518.6	0.0016	16	0.06	0.01	22	5	49	4	0.01	2	1.1	1.5	17	0.01
KL42-07	518.6	521.4	0.0074	74	0.04	0.01	52	26	35	5	0.01	0.01	0.7	1.7	13	0.01
KL42-07	521.4	524.5	0.0085	85	0.15	0.01	417	64	170	18	0.01	2	2.4	2.9	33	0.01
KL42-07	524.5	527.6	0.0069	69	0.11	0.01	246	41	110	16	0.01	3	1.6	2.7	24	0.01
KL42-07	527.6	530.6	0.001	10	0.01	0.01	49	12	19	11	0.01	2	0.5	1.0	18	0.01
KL42-07	530.6	533.6	0.0024	24	0.05	0.01	29	8	21	7	0.01	0.01	0.7	1.0	21	0.01
KL42-07	533.6	536.6	0.0017	17	0.03	0.01	32	7	21	6	0.01	0.01	0.6	0.9	15	0.01
KL42-07	536.6	539.6	0.0013	13	0.05	0.01	59	12	35	7	0.01	0.01	1	2.1	16	0.01
KL42-07	539.6	542.6	0.0009	9	0.03	0.01	24	8	13	5	0.01	0.01	0.4	1.3	11	0.01
KL42-07	542.6	545.6	0.0076	76	0.43	0.01	470	88	620	21	1	3	5.5	5.4	69	0.17
KL42-07	545.6	548.6	0.013	130	0.09	0.01	39	12	16	41	0.01	3	0.7	1.5	19	0.01
KL42-07	548.6	551.6	0.0037	37	0.15	0.01	124	33	110	11	0.01	2	1.9	1.8	30	0.01
KL42-07	551.6	554.6	0.007	70	0.37	0.01	520	105	200	16	1	3	3.7	4.0	46	0.1
KL42-07	554.6	557.6	0.0007	7	0.04	0.01	79	29	14	6	0.01	0.01	0.7	1.1	21	0.01
KL42-07	557.6	560.6	0.0008	8	0.01	0.01	43	15	7	4	0.01	0.01	0.5	0.9	15	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL42-07	560.6	563.6	0.0157		157	0.04	0.01	25	9	6	3	2	4	0.2	1.4	13	0.01
KL42-07	563.6	566.6	0.0006		6	0.02	0.01	24	9	4	4	0.01	0.01	0.01	1.2	14	0.01
KL42-07	566.6	569.6	0.0304		304	0.04	0.01	42	20	13	6	1	2	0.7	2.1	12	0.01
KL42-07	569.6	572.6	0.0008		8	0.01	0.01	32	9	8	5	0.01	3	0.01	1.2	11	0.01
KL42-07	572.6	575.6	0.0011		11	0.01	0.01	44	55	7	5	0.01	2	1.1	3.8	19	0.01
KL42-07	575.6	578.6	0.0104		104	0.01	0.01	39	10	6	5	0.01	2	0.01	2.3	12	0.01
KL42-07	578.6	581.6	0.0085		85	0.03	0.01	32	8	14	3	0.01	4	0.2	1.2	21	0.01
KL42-07	581.6	584	0.008		80	0.06	0.01	197	30	21	3	0.01	2	0.3	2.6	23	0.01
KL42-07	584	587.1	0.0029		29	0.04	0.01	261	50	15	6	0.01	2	2.3	1.4	17	0.01
KL42-07	587.1	588.2	0.0014		14	0.01	0.01	37	18	4	3	0.01	0.01	0.01	1.3	13	0.01
KL42-07	588.2	590.6	0.0012		12	0.01	0.01	15	16	2	3	0.01	0.01	0.01	1.0	13	0.01
KL42-08	0	3	0.001		10	0.03	1	267	172	6	5	0.01	0.01	2.3	0.0	17	0.01
KL42-08	3	5.1	0.0009		9	0.02	0.8	86	148	3	2	0.01	0.01	1.1	1.3	13	0.01
KL42-08	5.1	8.1	0.0013		13	0.02	1.2	96	198	2	2	0.01	0.01	1.7	1.1	16	0.01
KL42-08	8.1	11.1	0.0015		15	0.01	1.3	108	480	2	4	0.01	0.01	3.1	1.6	13	0.1
KL42-08	11.1	12.4	0.0012		12	0.01	1.3	93	470	2	4	0.01	0.01	3.3	2.0	14	0.1
KL42-08	12.4	14.7	0.0011		11	0.01	1.3	90	450	3	4	0.01	0.01	2.8	1.6	13	0.1
KL42-08	14.7	16.1	0.0104		104	0.28	4.9	1100	1060	110	13	10	3	8.6	24.0	29	0.14
KL42-08	16.1	18.8	0.0013		13	0.02	0.7	64	113	1	2	0.01	0.01	1.6	0.9	12	0.01
KL42-08	18.8	20.7	0.0051		51	0.04	4.3	216	140	16	0.01	1	0.01	4.2	1.7	19	0.22
KL42-08	20.7	22.6	0.0015		15	0.04	1.3	88	82	4	0.01	0.01	0.01	1.7	0.9	18	0.1
KL42-08	22.6	25	0.0023		23	0.02	1.6	61	95	5	0.01	0.01	0.01	2.1	0.7	13	0.15
KL42-08	25	26.7	0.0025		25	0.02	2.3	75	103	5	0.01	0.01	0.01	3.3	0.8	16	0.19
KL42-08	26.7	29	0.0022		22	0.04	1.1	95	201	6	0.01	0.01	0.01	1.8	0.9	12	0.1
KL42-08	29	32	0.0019		19	0.02	1.3	77	187	7	4	1	0.01	1.5	1.0	14	0.01
KL42-08	32	33.7	0.0013		13	0.01	0.8	70	78	2	2	0.01	0.01	1.1	0.6	12	0.01
KL42-08	33.7	35.7	0.0026		26	0.08	20.3	5100	14200	37	6	0.01	0.01	24	8.9	18	0.73
KL42-08	35.7	38.7	0.0015		15	0.03	1.1	174	180	3	5	0.01	0.01	2.4	1.2	16	0.11
KL42-08	38.7	41.7	0.001		10	0.02	1.2	348	1100	5	0.01	0.01	0.01	2.9	1.2	13	0.01
KL42-08	41.7	44.7	0.0019		19	0.07	11.2	2100	5000	19	3	0.01	0.01	16	5.0	15	0.31
KL42-08	44.7	47.7	0.0011		11	0.19	3	168	780	7	0.01	1	0.01	3	1.4	18	0.56
KL42-08	47.7	50.7	0.0006		6	0.03	0.01	48	96	3	0.01	0.01	0.01	0.9	0.0	15	0.01
KL42-08	50.7	53.7	0.0005		5	0.02	0.01	37	86	1	0.01	0.01	0.01	0.7	0.6	17	0.01
KL42-08	53.7	56.3	0.0007		7	0.03	0.01	48	121	2	0.01	0.01	0.01	0.8	0.0	18	0.01
KL42-08	56.3	59.4	0.0008		8	0.02	0.9	140	334	5	0.01	0.01	0.01	2.1	1.0	16	0.13
KL42-08	59.4	61.4	0.0006		6	0.08	2.3	265	840	3	0.01	0.01	0.01	1.9	1.2	16	0.21
KL42-08	61.4	62.2	0.0006		6	0.02	0.01	87	154	1	0.01	0.01	0.01	0.5	1.3	14	0.01
KL42-08	62.2	65.2	0.0012		12	0.02	1	90	207	7	0.01	0.01	0.01	3.7	0.6	16	0.01
KL42-08	65.2	67	0.0023		23	0.02	1.9	127	301	12	0.01	0.01	0.01	8.4	1.4	15	0.01
KL42-08	67	69.7	0.0005		5	0.02	0.6	48	79	8	0.01	0.01	0.01	0.9	0.0	16	0.01
KL42-08	69.7	71.7	0.0008		8	0.08	3.2	394	1380	8	0.01	0.01	0.01	3.6	1.6	17	0.4
KL42-08	71.7	74.6	0.0008		8	0.04	1.9	205	910	8	0.01	0.01	0.01	2.3	1.3	19	0.1
KL42-08	74.6	75.6	0.0023		23	0.02	1.9	1830	2840	6	0.01	0.01	0.01	3.3	12.6	19	0.01
KL42-08	75.6	78.7	0.0005		5	0.01	0.01	36	56	2	0.01	0.01	0.01	0.3	0.5	22	0.01
KL42-08	78.7	80.7	0.001		10	0.04	1.4	227	410	6	0.01	0.01	0.01	1.9	0.9	20	0.21
KL42-08	80.7	83.7	0.0007		7	0.11	2.5	287	600	10	0.01	0.01	0.01	2.9	1.1	18	0.35
KL42-08	83.7	86.7	0.0007		7	0.01	0.01	86	157	5	0.01	0.01	0.01	1	0.9	18	0.01
KL42-08	86.7	89.7	0.0006		6	0.03	1.2	195	440	9	0.01	0.01	0.01	1.3	1.4	21	0.01
KL42-08	89.7	92.7	0.0011		11	0.06	1.4	205	382	5	0.01	0.01	0.01	1.4	0.7	14	0.01
KL42-08	92.7	95.7	0.0007		7	0.04	0.6	67	68	4	0.01	0.01	0.01	0.5	0.0	17	0.01
KL42-08	95.7	98.7	0.0011		11	0.02	1.4	72	176	43	0.01	4	0.01	3.6	2.3	31	0.15
KL42-08	98.7	101.7	0.0014		14	0.01	0.6	98	104	10	0.01	0.01	0.01	0.8	0.8	19	0.01
KL42-08	101.7	104.7	0.0006		6	0.01	0.8	71	233	5	0.01	0.01	0.01	2.4	0.6	14	0.01
KL42-08	104.7	107.7	0.0132		132	0.05	3	720	990	28	4	2	0.01	5.1	5.8	25	0.1
KL42-08	107.7	110.7	0.0059		59	0.22	6	780	660	81	23	5	0.01	8.5	15.0	32	0.1
KL42-08	110.7	113.7	0.0046		46	0.02	1.4	178	262	10	3	2	0.01	1	1.6	40	0.01
KL42-08	113.7	116.7	0.0115		115	0.03	3	630	830	22	4	2	0.01	2.3	3.4	40	0.01
KL42-08	116.7	119.7	0.005		50	0.04	1.4	265	410	28	3	5	0.01	2.2	8.2	24	0.01
KL42-08	119.7	122.7	0.0022		22	0.02	3	211	800	28	5	4	0.01	4.5	2.1	30	0.01
KL42-08	122.7	125.7	0.0093		93	0.05	1	73	99	53	201	3	0.01	3.7	3.3	28	0.34
KL42-08	125.7	128.7	0.0016		16	0.13	1.4	57	130	35	26	3	0.01	4.3	1.7	20	0.14
KL42-08	128.7	131.7	0.0028		28	0.1	0.6	26	45	35	6	1	0.01	3.7	1.7	24	0.01
KL42-08	131.7	134.7	0.0018		18	0.01	0.7	53	74	31	24	2	0.01	2.1	3.4	24	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL42-08	134.7	137.7	0.0036		36	0.03	1.1	79	154	37	97	6	0.01	3	6.5	24	0.1
KL42-08	137.7	140.7	0.0062		62	0.01	0.9	161	149	28	28	2	2	2	4.1	24	0.1
KL42-08	140.7	143.7	0.0163		163	0.02	1.2	236	129	32	66	2	3	2.6	4.3	22	0.01
KL42-08	143.7	146.7	0.048		480	0.02	2.6	287	115	50	700	8	0.01	3.2	2.1	23	0.01
KL42-08	146.7	149.7	0.041		410	0.03	2.7	121	208	54	325	4	0.01	5.3	2.0	30	0.39
KL42-08	149.7	152.7	0.0135		135	0.05	1	71	73	43	90	1	2	5.1	3.1	34	0.47
KL42-08	152.7	155.7	0.041		410	0.03	2.5	124	190	46	320	4	0.01	5.8	2.5	31	0.4
KL42-08	155.7	158.7	0.0046		46	0.06	3	297	351	26	9	2	0.01	3.2	10.6	24	0.39
KL42-08	158.7	161.7	0.0125		125	0.12	10.3	1180	800	81	30	10	5	5.4	30.3	41	0.16
KL42-08	161.7	164.7	0.049		490	0.19	18.2	3400	4880	120	57	40	8	6.5	93.0	105	0.01
KL42-08	164.7	167.7	0.0158		158	0.07	7.9	1160	1450	65	32	13	5	3.7	37.0	62	0.01
KL42-08	167.7	170.7	0.0108		108	0.05	3.7	590	700	65	17	6	0.01	3.5	20.0	45	0.01
KL42-08	170.7	173.7	0.0158		158	0.08	6.3	1060	1350	75	24	12	3	3.9	34.0	55	0.01
KL42-08	173.7	176.7	0.056		560	0.11	9	3100	3850	140	12	7	2	12	19.0	45	0.01
KL42-08	176.7	179.7	0.052		520	0.3	13.7	2000	1100	240	27	50	2	12	74.0	38	0.17
KL42-08	179.7	182.7	0.079		790	0.36	12.8	4520	1180	190	34	36	3	14	137.0	40	0.29
KL42-08	182.7	185.7	0.043		430	0.47	15.1	730	1260	310	73	44	5	9.4	182.0	78	0.01
KL42-08	185.7	188.7	0.0108		108	0.18	4.8	730	940	78	16	7	0.01	4.5	32.0	27	0.16
KL42-08	188.7	191.7	0.0146		146	0.12	3.7	286	480	120	23	2	2	8.2	23.0	38	0.01
KL42-08	191.7	194.7	0.0126		126	0.16	8.4	1140	1480	92	22	24	0.01	5.8	68.0	45	0.12
KL42-08	194.7	197.7	0.053		530	0.33	13.9	1910	1050	250	29	42	2	12	58.0	46	0.29
KL42-08	197.7	200.7	0.0272		272	0.11	11.8	1670	1580	93	32	46	2	4.3	74.0	90	0.01
KL42-08	200.7	203.7	0.0079		79	0.09	6.5	750	1100	69	11	18	2	3.6	28.0	35	0.1
KL42-08	203.7	206.7	0.044		440	0.02	11.9	4070	1980	40	79	30	10	2.5	35.5	60	0.01
KL42-08	206.7	209.7	0.107		1070	0.07	23.8	8000	700	140	207	62	16	6.1	89.0	82	0.01
KL42-08	209.7	212.7	0.143		1430	0.24	13.3	9800	2500	48	980	45	20	2.8	58.5	37	0.01
KL42-08	212.7	215.7	0.005		50	0.05	1.5	335	800	53	990	3	0.01	2.3	10.7	16	0.01
KL42-08	215.7	218.7	0.0028		28	0.1	0.6	126	82	68	870	3	0.01	2.6	11.7	41	0.01
KL42-08	218.7	221.7	0.005		50	0.08	3.2	740	1590	88	30	3	3	10.4	5.9	37	0.01
KL42-08	221.7	224.7	0.0196		196	0.12	3.1	850	940	58	294	9	3	5.3	26.2	31	0.01
KL42-08	224.7	227.7	0.0079		79	0.19	16.2	1110	2670	120	6	1	0.01	40	10.5	21	0.14
KL42-08	227.7	230.7	0.0155		155	0.31	2	490	340	140	29	5	3	9.8	10.4	24	0.2
KL42-08	230.7	233.7	0.0025		25	0.08	1.3	93	341	21	2	0.01	0.01	7.1	4.4	12	0.1
KL42-08	233.7	236.7	0.0068		68	0.12	3.6	810	1500	83	75	5	4	9.8	7.3	46	0.01
KL42-08	236.7	239.7	0.006		60	0.14	7.2	730	1400	80	56	5	4	14.4	7.4	42	0.1
KL42-08	239.7	242.7	0.0076		76	0.24	9.8	1140	740	85	17	7	2	10.9	12.1	35	0.01
KL42-08	242.7	244.9	0.0025		25	0.11	1.1	111	430	120	7	0.01	0.01	3.9	3.5	30	0.12
KL42-08	244.9	247.9	0.0055		55	0.06	0.7	161	339	76	3	0.01	0.01	2.4	2.3	32	0.1
KL42-08	247.9	250.9	0.0035		35	0.05	1.7	560	1380	82	3	0.01	3	4.5	2.7	38	0.01
KL42-08	250.9	253.9	0.0028		28	0.15	2.4	414	1480	180	50	0.01	3	9.5	4.2	41	0.25
KL42-08	253.9	257	0.0044		44	0.04	1.9	112	1000	83	3	0.01	3	3.9	6.5	35	0.01
KL42-08	257	260.1	0.0031		31	0.04	2.3	101	1250	74	4	0.01	3	4.3	5.4	43	0.01
KL42-08	260.1	263.2	0.0266		266	0.1	29.7	9600	7600	260	22	6	0.01	70	7.8	16	0.61
KL42-08	263.2	266.3	0.0022		22	0.1	2.1	156	1180	54	15	4	0.01	4.7	9.2	29	0.1
KL42-08	266.3	269.4	0.0021		21	0.08	3.5	440	2480	75	5	0.01	3	7.3	11.6	38	0.17
KL42-08	269.4	272.3	0.0038		38	0.07	6.9	510	5020	62	6	2	2	9.1	42.0	27	0.01
KL42-08	272.3	275.3	0.0019		19	0.1	1.9	139	1480	100	7	4	4	4	17.8	41	0.01
KL42-08	275.3	278.4	0.0084		84	0.17	4.8	140	5300	100	22	3	7	11.8	72.5	62	0.01
KL42-08	278.4	281.4	0.0097		97	0.09	3.9	450	560	83	120	15	5	3.9	10.9	35	0.01
KL42-08	281.4	284.5	0.0065		65	0.06	8.7	3780	5500	90	66	8	2	7.6	12.8	26	0.01
KL42-08	284.5	287.6	0.0032		32	0.07	3.7	301	1340	52	24	3	4	40	5.2	16	0.1
KL42-08	287.6	290.7	0.0016		16	0.06	1.1	251	383	39	2	0.01	0.01	6.4	2.3	10	0.01
KL42-08	290.7	293.7	0.0053		53	0.1	3.9	2120	2360	40	22	8	2	6.6	9.5	16	0.01
KL42-08	293.7	296.7	0.0036		36	0.06	1.6	600	1420	81	3	0.01	3	4.3	1.8	35	0.1
KL42-08	296.7	299.7	0.002		20	0.03	1.5	160	326	58	49	5	9	2.3	6.3	20	0.01
KL42-08	299.7	302.7	0.0007		7	0.05	0.7	45	56	5	2	0.01	0.01	0.5	0.8	15	0.01
KL42-08	302.7	305.7	0.0008		8	0.02	0.6	117	318	5	2	0.01	0.01	2.6	0.8	12	0.12
KL42-08	305.7	308.7	0.0049		49	0.02	4.6	201	470	40	5	0.01	3	18	3.6	24	0.01
KL42-08	308.7	311.7	0.0067		67	0.22	9.2	1000	800	88	23	6	3	16	10.9	35	0.12
KL42-08	311.7	314.7	0.0039		39	0.21	4.5	610	690	61	28	8	2	7.7	10.5	28	0.01
KL42-08	314.7	317.7	0.0071		71	0.32	4.6	1180	1080	130	21	11	4	12	8.3	25	0.13
KL42-08	317.7	320.7	0.0104		104	0.21	12.1	2470	5800	150	20	4	5	24	8.3	30	0.11
KL42-08	320.7	323.7	0.0067		67	0.19	1.6	500	300	160	35	5	5	7.7	5.0	37	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL42-08	323.7	326.7	0.0062		62	0.18	1.9	530	304	150	30	4	6	10	6.9	37	0.01
KL42-08	326.7	329.7	0.0379		379	0.76	42	3260	2230	350	57	14	5	40	31.3	56	0.22
KL42-08	329.7	332.7	0.0077		77	0.41	12	1700	920	120	57	8	4	12.6	30.5	53	0.1
KL42-08	332.7	335.7	0.049		490	0.72	51	4550	2800	370	56	14	4	46	35.8	61	0.29
KL42-08	335.7	338.7	0.011		110	0.35	5.4	1320	1700	78	20	13	2	13.5	39.0	28	0.21
KL42-08	338.7	341.7	0.0142		142	0.12	4	890	1400	71	107	6	2	10.1	8.6	30	0.1
KL42-08	341.7	344.7	0.0186		186	0.13	3.3	910	1150	76	280	6	4	6.4	16.5	32	0.1
KL42-08	344.7	347.7	0.0394		394	0.28	49	51900	78200	130	29	5	3	70	293.0	27	0.14
KL42-08	347.7	350.7	0.102		1020	0.43	96	6800	17500	580	15	8	0.01	410	29.5	18	0.5
KL42-08	350.7	353.7	0.006		60	0.2	10.3	950	2270	110	7	1	0.01	23.5	6.3	23	0.14
KL42-08	353.7	356.7	0.0108		108	0.13	5.6	1250	1680	140	9	4	0.01	18	5.2	8	0.3
KL42-08	356.7	359.7	0.0036		36	0.08	4	346	1430	50	12	1	0.01	50	4.9	14	0.01
KL42-08	359.7	362.7	0.0118		118	0.7	42	15500	10000	94	116	13	0.01	17.8	144.0	31	0.01
KL42-08	362.7	364.2	0.0011		11	0.06	1	207	162	16	5	0.01	0.01	2.1	1.7	14	0.01
KL42-08	364.2	367	0.0012		12	0.05	0.9	300	400	22	3	2	0.01	2.9	4.5	10	0.01
KL42-08	367	370.1	0.0021		21	0.06	1.9	620	620	34	31	6	0.01	2.9	6.5	21	0.01
KL42-08	370.1	371.6	0.0028		28	0.06	1.3	710	460	30	47	6	0.01	6.6	6.3	23	0.01
KL42-08	371.6	374.6	0.0255		255	0.09	32	10600	8800	230	30	6	0.01	70	7.6	13	0.56
KL42-08	374.6	377.6	0.0125		125	0.77	15.6	3500	6400	1000	14	4	10	80	18.2	35	0.96
KL42-08	377.6	380.7	0.0125		125	0.78	15.4	3540	6000	980	15	3	11	80	18.5	36	0.85
KL42-08	380.7	383.7	0.017		170	0.92	14	3440	3210	1140	27	9	8	90	14.0	32	0.89
KL42-08	383.7	386.1	0.002		20	0.07	1.4	256	440	57	2	0.01	0.01	9.4	2.0	13	0.01
KL42-08	386.1	389.2	0.0396		396	0.08	1.3	1610	181	84	4	1	2	3.2	6.4	10	0.29
KL42-08	389.2	392.3	0.0039		39	0.06	1.3	570	236	50	5	1	0.01	2.8	3.9	10	0.01
KL42-08	392.3	394.4	0.124		1240	0.11	1.4	3550	170	160	9	1	4	3.8	9.1	14	0.49
KL42-08	394.4	396	0.321		3210	0.02	2.6	135	99	200	34	3	26	2.8	2.8	23	0.01
KL42-08	396	398.5	0.0084		84	0.01	0.01	100	146	120	13	1	15	1.4	3.3	17	0.01
KL42-08	398.5	401.6	0.0125		125	0.01	0.6	46	45	40	100	2	13	1.5	2.3	13	0.01
KL42-08	401.6	404.5	0.002		20	0.04	2.2	153	286	52	49	5	8	2.2	9.1	21	0.01
KL42-08	404.5	407.6	0.004		40	0.02	1.7	212	1610	85	10	2	10	2.8	11.2	16	0.01
KL42-09	0	5.2	0.0125		125	0.05	0.9	157	101	9	7	0.01	0.01	1.6	4.7	19	0.16
KL42-09	5.2	8.6	0.0045		45	0.12	1.8	520	390	20	7	0.01	0.01	2.6	1.9	16	0.1
KL42-09	8.6	11.6	0.0041		41	0.04	1.5	284	323	10	5	0.01	0.01	2.3	1.5	14	0.01
KL42-09	11.6	14.9	0.0039		39	0.06	2.3	1390	420	13	2	0.01	0.01	3.2	1.6	18	0.01
KL42-09	14.9	17.4	0.0041		41	0.1	1.1	269	122	9	4	0.01	0.01	2.2	1.4	21	0.18
KL42-09	17.4	20.6	0.0054		54	0.07	1.2	206	86	15	7	0.01	0.01	1.8	0.9	20	0.1
KL42-09	20.6	23.6	0.003		30	0.08	3.5	430	298	28	3	0.01	0.01	3.2	1.3	17	0.31
KL42-09	23.6	26.6	0.0034		34	0.07	0.7	110	56	9	2	0.01	0.01	1.5	0.7	21	0.1
KL42-09	26.6	29.6	0.003		30	0.08	0.01	66	57	12	6	0.01	0.01	1.8	0.9	19	0.01
KL42-09	29.6	32.6	0.0019		19	0.04	0.01	74	48	6	0.01	0.01	0.01	3	1.3	14	0.01
KL42-09	32.6	35.6	0.0059		59	0.03	0.5	81	36	12	6	0.01	0.01	3.2	2.5	25	0.01
KL42-09	35.6	38.6	0.0022		22	0.04	0.8	60	129	8	4	1	0.01	1.8	1.7	34	0.01
KL42-09	38.6	41.6	0.0031		31	0.13	2.2	830	130	21	4	0.01	0.01	6.2	1.3	45	0.98
KL42-09	41.6	44.6	0.0025		25	0.12	2.6	650	151	24	5	0.01	0.01	4.8	3.0	23	0.75
KL42-09	44.6	47.6	0.0017		17	0.1	1.6	960	450	17	7	0.01	0.01	4.7	2.3	19	1.1
KL42-09	47.6	50.6	0.0035		35	0.11	0.9	166	60	27	4	0.01	0.01	8	0.0	60	0.55
KL42-09	50.6	53.6	0.0038		38	0.01	0.01	37	13	10	2	0.01	0.01	1.6	0.0	31	0.01
KL42-09	53.6	56.6	0.0027		27	0.04	0.6	48	24	12	2	0.01	0.01	2.8	0.8	23	0.14
KL42-09	56.6	59.6	0.003		30	0.01	0.01	35	22	8	3	0.01	0.01	1.3	0.8	17	0.01
KL42-09	59.6	62.6	0.0046		46	0.01	0.01	77	47	13	5	0.01	0.01	1.8	1.0	20	0.01
KL42-09	62.6	65.6	0.0022		22	0.01	0.01	29	15	11	2	0.01	0.01	0.9	1.4	21	0.01
KL42-09	65.6	68.6	0.0015		15	0.01	0.5	23	12	10	4	0.01	0.01	0.6	0.9	30	0.01
KL42-09	68.6	71.6	0.0093		93	0.01	0.01	26	24	29	3	0.01	0.01	6.3	1.1	31	0.01
KL42-09	71.6	74.6	0.012		120	0.01	0.01	26	8	7	4	0.01	0.01	0.6	1.2	23	0.01
KL42-09	74.6	77.6	0.0012		12	0.01	0.01	15	15	13	4	0.01	0.01	0.5	2.1	24	0.01
KL42-09	77.6	80.6	0.0032		32	0.02	0.8	74	37	18	9	0.01	0.01	1.8	1.6	26	0.01
KL42-09	80.6	83.6	0.0032		32	0.01	0.01	68	24	6	3	0.01	0.01	0.6	0.7	31	0.01
KL42-09	83.6	86.6	0.0038		38	0.01	0.01	29	13	9	3	0.01	0.01	0.8	0.7	44	0.01
KL42-09	86.6	89.6	0.0019		19	0.03	0.6	344	133	5	2	0.01	0.01	1.3	1.5	34	0.25
KL42-09	89.6	92.6	0.0027		27	0.03	1.2	258	192	21	4	0.01	0.01	2	2.1	28	0.11
KL42-09	92.6	95.6	0.0031		31	0.01	0.01	68	37	18	4	0.01	0.01	0.9	1.4	29	0.01
KL42-09	95.6	98.6	0.0011		11	0.01	0.01	45	42	17	3	0.01	0.01	0.7	1.2	30	0.01
KL42-09	98.6	101.4	0.0012		12	0.03	0.8	159	117	31	3	0.01	0.01	3.6	2.8	15	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL42-09	101.4	104.5	0.0192		192	0.05	2.2	430	420	59	22	5	0.01	10	3.1	26	0.15
KL42-09	104.5	107.6	0.0095		95	0.01	2.9	2080	1900	35	7	0.01	0.01	11.9	2.9	24	0.18
KL42-09	107.6	110.6	0.21		2100	0.04	73	63000	54900	51	5	0.01	0.01	200	80.0	17	2.65
KL42-09	110.6	113.6	0.0063		63	0.01	1.7	376	510	19	3	0.01	0.01	5.7	1.8	27	0.01
KL42-09	113.6	116.6	0.0013		13	0.01	0.5	83	106	8	4	0.01	2	1.6	1.1	20	0.01
KL42-09	116.6	119.1	0.0018		18	0.01	1.9	34	33	9	3	0.01	2	0.5	1.6	26	0.01
KL42-09	119.1	122.6	0.0029		29	0.01	0.7	800	640	8	10	0.01	0.01	1.6	4.1	15	0.01
KL42-09	122.6	125.6	0.0036		36	0.04	5.5	760	1440	46	2	0.01	0.01	33	1.7	26	0.44
KL42-09	125.6	128.6	0.0041		41	0.06	16.5	780	2480	69	3	2	0.01	82	4.5	19	0.47
KL42-09	128.6	131.6	0.0011		11	0.04	1.6	480	322	28	2	0.01	0.01	28	1.8	14	0.26
KL42-09	131.6	134.6	0.0012		12	0.01	0.5	100	61	8	4	0.01	0.01	2.4	1.1	21	0.01
KL42-09	134.6	137.6	0.0014		14	0.01	0.01	36	44	4	4	0.01	0.01	0.8	0.0	20	0.01
KL42-09	137.6	140.6	0.004		40	0.01	1	156	61	6	3	0.01	0.01	2.9	1.6	12	0.01
KL42-09	140.6	143.6	0.0009		9	0.04	0.01	68	33	22	2	0.01	0.01	1.8	1.4	25	0.01
KL42-09	143.6	146.6	0.0036		36	0.15	0.8	50	47	41	8	1	0.01	3.3	2.7	18	0.11
KL42-09	146.6	149.6	0.0026		26	0.24	0.9	336	211	21	4	0.01	0.01	7.5	3.2	36	0.01
KL42-09	149.6	152.6	0.001		10	0.11	0.7	291	119	21	4	0.01	0.01	3.3	4.9	19	0.01
KL42-09	152.6	155.6	0.0023		23	0.01	0.01	450	345	18	2	0.01	0.01	1.5	1.0	24	0.01
KL42-09	155.6	158.6	0.0043		43	0.07	6.1	4000	4500	49	10	6	0.01	8.4	17.5	40	0.37
KL42-09	158.6	161.6	0.168		1680	0.28	13.3	570	490	330	12	134	0.01	43	20.0	46	0.39
KL42-09	161.6	164.6	0.003		30	0.09	1.3	307	270	20	3	2	0.01	3.4	2.4	24	0.01
KL42-09	164.6	167.6	0.0042		42	0.17	5.5	910	2260	62	3	1	0.01	10.3	3.5	29	0.01
KL42-09	167.6	170.6	0.122		1220	0.18	2.6	1000	880	210	6	0.01	0.01	4.9	4.9	33	0.11
KL42-09	170.6	173.6	0.0038		38	0.03	0.8	2500	1250	15	2	0.01	0.01	2.1	1.7	20	0.1
KL42-09	173.6	176.6	0.0068		68	0.03	2.9	1830	1050	23	2	6	0.01	3.1	3.3	33	0.01
KL42-09	176.6	179.6	0.0063		63	0.07	12	3300	2130	44	24	39	3	3.6	16.2	42	0.11
KL42-09	179.6	182.6	0.057		570	0.25	5.1	3750	5000	140	10	9	6	11	5.8	48	0.4
KL42-09	182.6	185.1	0.099		990	0.14	3.6	187	259	310	13	50	2	35	7.5	47	0.29
KL42-09	185.1	188.2	0.0367		367	0.07	13.4	4700	3200	110	9	8	3	64	12.0	43	0.67
KL42-09	188.2	190.9	0.048		480	0.16	7.5	5500	2600	200	140	17	5	26	16.4	24	0.33
KL42-09	190.9	192.8	3.27		32700	2.32	60	520	540	8000	7	372	58	3400	102.0	165	3.25
KL42-09	192.8	195.2	1.67		16700	1.02	30	238	121	4900	51	63	26	780	25.5	135	1.38
KL42-09	195.2	197.1	0.92		9200	1.64	48	580	296	3300	112	24	3	440	18.8	235	1.35
KL42-09	197.1	200.3	0.34		3400	0.6	72	111	232	650	10	100	0.01	180	53.2	88	0.38
KL42-09	200.3	203.4	0.08		800	1.03	63	720	14600	680	13	19	0.01	93	13.8	123	1.16
KL42-09	203.4	206.5	0.0183		183	0.38	3.2	5900	2000	170	8	7	2	10.5	4.8	198	0.1
KL42-09	206.5	208.7	0.0237		237	1.28	14.1	11600	13100	200	39	4	3	23.5	16.0	103	0.21
KL42-09	208.7	211.6	0.08		800	1.34	41	5300	27600	350	89	4	4	49	29.7	135	0.39
KL42-09	211.6	214.6	0.024		240	0.09	3.6	1320	1330	59	18	2	0.01	16.1	1.6	125	0.15
KL42-09	214.6	218.6	0.0111		111	0.19	2.3	2430	930	57	22	3	0.01	6.6	1.9	200	0.01
KL42-09	218.6	221.6	0.0041		41	0.22	2.4	2050	1680	63	31	1	0.01	5.6	1.9	90	0.01
KL42-09	221.6	224.6	0.047		470	0.08	3.1	1520	810	78	32	20	2	18.7	2.4	110	0.01
KL42-09	224.6	227.6	0.0176		176	0.07	2.3	1040	610	49	36	5	2	6.7	1.3	97	0.01
KL42-09	227.6	230.4	0.0082		82	0.48	4.8	3950	2500	75	14	1	0.01	9.1	2.4	110	0.1
KL42-09	230.4	233.5	0.0137		137	0.26	2.5	4300	1240	53	31	1	0.01	5.9	2.4	183	0.01
KL42-09	233.5	236.6	0.095		950	0.2	6.1	4000	5000	320	99	3	2	48	7.0	141	0.15
KL42-09	236.6	239.6	0.0061		61	0.24	1.2	860	480	18	20	1	0.01	2.5	3.3	71	0.01
KL42-09	239.6	242.3	0.0031		31	0.2	1.4	420	450	30	15	1	0.01	3.3	1.9	80	0.01
KL42-09	242.3	245.4	0.0056		56	0.1	1	152	298	23	321	2	0.01	2.9	2.6	50	0.01
KL42-09	245.4	247.9	0.0075		75	0.18	175	610	45600	33	37	400	0.01	10.4	307.0	50	0.01
KL42-09	247.9	250.7	0.0051		51	0.04	3.1	175	1950	34	150	8	0.01	6.5	18.1	86	0.01
KL42-09	250.7	253.9	0.0106		106	0.02	4.6	145	1610	50	188	15	0.01	8	17.5	14	0.01
KL42-09	253.9	256.6	0.0198		198	0.06	4.9	198	1400	64	450	29	2	9.5	14.0	55	0.01
KL42-09	256.6	258.9	0.444		4440	0.3	5	1140	670	1200	1750	41	11	82	7.4	76	0.36
KL42-09	258.9	261.1	0.98		9800	1.09	16.3	3200	1280	1320	1480	246	29	170	22.5	77	0.48
KL42-09	261.1	263.6	0.064		640	0.54	6.8	2970	1340	210	200	39	6	37	40.3	64	0.29
KL42-09	263.6	266.6	0.0242		242	0.08	4.3	1630	1430	32	34	27	2	3.8	10.4	16	0.14
KL42-09	266.6	269.6	0.0174		174	0.08	2	384	720	35	26	10	0.01	1.9	6.0	17	0.01
KL42-09	269.6	272.6	0.0112		112	0.08	4.1	132	1210	31	9	12	0.01	1.9	5.8	15	0.01
KL42-09	272.6	275.6	0.0072		72	0.04	1	67	460	15	10	4	0.01	1.1	2.6	13	0.01
KL42-09	275.6	278.3	0.01		100	0.07	1.5	102	540	45	7	5	0.01	3.2	4.6	12	0.01
KL42-09	278.3	281.5	0.0063		63	0.05	1.7	117	580	28	6	6	0.01	1.8	5.0	17	0.01
KL42-09	281.5	284.6	0.0239		239	0.17	28.4	3200	10500	80	4	100	0.01	19.5	13.0	37	0.15

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL42-09	284.6	287.6	0.0043		43	0.03	1.2	69	192	8	5	2	0.01	1.3	1.8	22	0.01
KL42-09	287.6	290.3	0.0018		18	0.02	0.01	48	36	8	4	1	0.01	0.4	0.5	24	0.01
KL42-09	290.3	293.3	0.0105		105	0.07	2.3	2580	710	16	8	14	0.01	1.2	10.3	27	0.01
KL42-09	293.3	296.7	0.0037		37	0.03	1.1	660	301	10	9	4	0.01	1.2	2.5	27	0.01
KL42-09	296.7	299.4	0.0025		25	0.05	1.4	283	287	17	5	3	0.01	1.3	3.5	27	0.01
KL42-09	299.4	301.9	0.0066		66	0.05	2.5	1820	1250	29	4	7	0.01	3.4	8.3	26	0.16
KL42-09	301.9	304.6	0.002		20	0.02	0.6	96	90	9	10	2	0.01	0.7	1.3	21	0.01
KL42-09	304.6	307.4	0.0103		103	0.09	3.9	660	1650	36	30	7	0.01	8.8	6.3	30	0.01
KL42-09	307.4	309.7	0.054		540	0.09	4.2	177	301	180	16	5	0.01	26	4.8	38	0.01
KL42-09	309.7	312.2	0.003		30	0.04	1.1	70	76	13	7	4	0.01	0.9	3.0	34	0.01
KL42-09	312.2	314.8	0.0174		174	0.06	3.2	218	216	67	15	7	0.01	2.8	9.3	34	0.01
KL42-09	314.8	317.2	0.022		220	0.14	3.3	670	237	120	21	9	0.01	5.5	15.1	60	0.01
KL42-09	317.2	320.2	0.0039		39	0.03	1.3	112	225	11	4	4	0.01	0.7	9.3	31	0.01
KL42-09	320.2	323.2	0.005		50	0.02	0.8	97	52	16	9	2	0.01	0.9	4.0	29	0.01
KL42-09	323.2	326.6	0.0127		127	0.06	5.7	4810	3870	18	11	8	0.01	7.8	9.5	28	0.17
KL42-09	326.6	329.3	0.0082		82	0.03	1.2	520	204	23	25	4	0.01	5	2.0	21	0.01
KL42-09	329.3	331.7	0.0056		56	0.02	0.6	103	65	16	40	2	0.01	1.8	1.5	17	0.01
KL42-09	331.7	334.8	0.001		10	0.02	0.01	62	53	3	13	1	0.01	0.4	1.5	12	0.01
KL42-09	334.8	337.1	0.0013		13	0.01	0.8	94	201	3	15	3	0.01	0.4	2.8	10	0.01
KL42-09	337.1	339.3	0.0044		44	0.02	0.6	209	87	10	24	2	0.01	5	2.8	14	0.01
KL42-09	339.3	342.6	0.0017		17	0.01	0.7	229	245	3	10	1	0.01	0.4	2.3	13	0.01
KL42-09	342.6	345.1	0.001		10	0.01	0.01	122	68	1	10	1	0.01	0.3	1.8	15	0.01
KL42-09	345.1	348.8	0.0013		13	0.01	0.01	129	88	3	6	1	0.01	0.4	1.3	16	0.01
KL42-09	348.8	351.6	0.0021		21	0.01	0.01	85	68	5	5	1	0.01	0.8	1.8	16	0.01
KL42-09	351.6	354.1	0.0033		33	0.01	1.3	341	1060	12	8	2	0.01	1.8	3.8	17	0.01
KL42-09	354.1	356.6	0.0012		12	0.01	0.01	182	80	4	5	1	0.01	0.3	1.9	14	0.01
KL42-09	356.6	359.2	0.0036		36	0.01	0.9	680	363	8	4	2	0.01	0.5	2.8	15	0.01
KL42-09	359.2	362.6	0.002		20	0.02	0.01	190	126	8	11	1	0.01	0.8	2.5	15	0.01
KL42-09	362.6	365.6	0.0083		83	0.06	4.5	960	17800	38	10	110	0.01	8.5	192.0	23	0.01
KL42-09	365.6	368.6	0.026		260	0.02	4.2	830	1320	12	17	1	0.01	1.5	11.8	15	0.01
KL42-09	368.6	371.6	0.0048		48	0.04	0.9	90	206	6	4	1	0.01	1.6	2.5	20	0.01
KL42-09	371.6	374.5	0.0106		106	0.02	1.2	316	770	17	9	2	0.01	1.6	3.5	17	0.01
KL42-09	374.5	377.6	0.0183		183	0.03	1.3	490	580	2	123	5	0.01	2.9	4.3	16	0.01
KL42-09	377.6	380.6	0.0124		124	0.02	2.3	290	1000	16	7	2	0.01	7.6	6.5	17	0.01
KL42-09	380.6	382.9	0.004		40	0.01	0.01	81	97	2	4	1	0.01	0.5	1.5	14	0.01
KL42-09	382.9	384.9	0.0074		74	0.02	0.8	540	720	5	5	1	0.01	1.4	4.3	13	0.01
KL42-09	384.9	386.8	0.05		500	0.06	0.8	395	383	9	35	1	0.01	1.2	4.8	14	0.01
KL42-09	386.8	389.6	0.52		5200	0.24	1.4	520	22	8	320	4	28	0.2	4.8	14	0.01
KL42-09	389.6	392.6	0.0075		75	0.01	0.9	1140	780	5	16	0.01	0.01	1.7	3.5	18	0.01
KL42-09	392.6	395.6	0.0099		99	0.02	1.2	550	750	9	10	1	0.01	1.8	7.3	12	0.11
KL42-09	395.6	398.6	1.32		13200	0.37	2.6	580	17	25	46	2	27	1	9.5	26	0.01
KL42-09	398.6	401.6	0.22		2200	0.53	13.8	24600	5000	230	13	46	10	5.3	96.0	36	0.85
KL42-09	401.6	404.6	0.42		4200	0.53	2.7	217	88	110	15	3	12	10.5	25.6	51	0.01
KL42-09	404.6	407.6	1.49		14900	1.33	2.9	151	40	32	33	0.01	11	3.6	12.0	41	0.01
KL42-09	407.6	410.6	1.81		18100	1.16	2.6	146	27	8	23	0.01	7	1.6	8.5	30	0.01
KL42-09	410.6	412.4	0.336		3360	0.25	1.2	157	70	23	39	1	10	1.5	4.5	60	0.01
KL42-09	412.4	414.9	0.89		8900	1.09	2.6	189	30	29	7	2	18	8.3	12.5	32	0.01
KL42-09	414.9	417.6	1.45		14500	1.44	4.7	257	45	13	17	4	20	5.5	17.2	41	0.01
KL42-09	417.6	419.6	0.059		590	0.08	1.3	2650	740	59	7	4	3	8.6	10.5	15	0.26
KL42-09	419.6	420.8	1.41		14100	0.32	2.1	346	27	7	23	16	16	0.5	4.5	23	0.01
KL42-09	420.8	423	0.375		3750	0.39	1.4	103	33	22	19	1	7	0.6	4.3	16	0.01
KL42-09	423	425.6	0.75		7500	0.44	1.9	101	20	14	59	1	12	1.2	6.5	9	0.01
KL42-09	425.6	428.6	0.37		3700	0.36	1.1	157	59	25	45	1	10	1.2	4.5	51	0.01
KL42-09	428.6	431.6	0.192		1920	0.04	1.8	127	88	89	23	5	5	13.8	3.3	142	0.01
KL42-09	431.6	434.3	0.14		1400	0.15	0.7	41	10	5	37	1	0.01	0.7	1.5	10	0.01
KL42-09	434.3	437.4	0.062		620	0.07	0.01	56	9	5	92	1	0.01	0.6	0.0	29	0.01
KL42-09	437.4	440.6	1.33		13300	0.15	1.9	770	11	2	11	2	25	0.8	7.5	21	0.01
KL42-09	440.6	443.6	1.91		19100	0.29	3.1	520	15	4	257	1	31	0.01	8.5	31	0.01
KL42-09	443.6	446.6	0.057		570	0.04	0.7	1100	220	9	8	0.01	6	0.8	6.5	25	0.01
KL42-09	446.6	449.6	1.54		15400	0.32	2.3	8900	20	11	530	1	41	1.1	10.0	20	0.01
KL42-09	449.6	452.6	0.47		4700	0.23	1.2	1800	15	7	8	1	30	0.2	6.3	11	0.01
KL42-09	452.6	455.6	0.49		4900	0.23	1.1	650	17	13	9	0.01	31	0.6	6.0	21	0.01
KL42-09	455.6	458.6	0.45		4500	0.23	1	610	12	13	8	0.01	33	0.7	6.0	21	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL42-09	458.6	461.6	0.0152		152	0.01	0.01	40	15	4	12	0.01	0.01	0.9	0.0	7	0.01
KL42-09	461.6	464.6	0.063		630	0.04	0.7	640	45	20	3	2	5	0.01	3.3	13	0.01
KL42-09	464.6	467.1	0.072		720	0.08	0.01	261	17	15	4	1	6	0.2	2.5	20	0.01
KL42-09	467.1	470.2	0.0378		378	0.02	0.01	32	20	4	60	1	2	0.6	1.6	205	0.01
KL42-09	470.2	473.1	2.22		22200	0.28	2.6	417	10	3	1020	1	26	1.2	1.0	15	0.01
KL42-09	473.1	474.6	2.47		24700	0.38	2.8	820	9	4	1660	1	46	0.3	12.5	19	0.01
KL42-09	474.6	477.6	0.27		2700	0.13	2	1360	970	18	14	0.01	4	4.2	3.3	13	0.01
KL42-09	477.6	479.6	0.92		9200	0.45	1.2	118	20	7	16	0.01	5	0.3	10.5	17	0.01
KL42-09	479.6	482.6	0.102		1020	0.09	0.01	2910	15	16	20	0.01	23	2.6	2.0	16	0.01
KL42-09	482.6	485.6	0.108		1080	0.07	0.01	236	16	8	158	2	4	0.9	1.3	42	0.01
KL42-09	485.6	488.6	0.287		2870	0.17	1.4	302	221	14	323	0.01	4	0.01	4.5	19	0.01
KL42-09	488.6	491.6	0.4		4000	0.14	3.4	960	650	14	48	2	4	0.8	4.0	14	0.01
KL42-09	491.6	494.6	0.125		1250	0.07	0.8	238	13	20	13	6	3	0.2	0.8	16	0.01
KL42-09	494.6	497.6	0.043		430	0.04	0.6	268	46	17	5	0.01	0.01	0.3	0.8	13	0.01
KL42-09	497.6	499.6	0.094		940	0.1	0.9	231	39	18	6	2	0.01	0.3	1.8	16	0.01
KL42-09	499.6	502.8	0.282		2820	0.13	1	289	61	13	9	1	7	0.01	3.0	13	0.01
KL42-09	502.8	504.8	0.066		660	0.07	0.5	430	51	25	5	2	0.01	0.7	1.0	16	0.01
KL42-09	504.8	507	0.076		760	0.07	0.9	324	85	12	6	1	2	1.5	1.3	20	0.01
KL42-09	507	509	1.15		11500	0.6	3.8	1280	88	17	7	1	12	0.7	13.0	27	0.01
KL42-09	509	512.6	1.17		11700	0.78	4.3	2600	720	17	7	0.01	18	2	10.2	27	0.01
KL42-09	512.6	515.6	0.75		7500	0.75	2.6	394	54	21	9	1	20	1.7	7.8	28	0.01
KL42-09	515.6	518.6	0.47		4700	0.44	2.5	480	50	24	4	1	17	1.3	7.8	31	0.01
KL42-09	518.6	521.6	0.228		2280	0.23	2.1	470	265	9	8	1	10	1.6	4.3	84	0.01
KL42-09	521.6	524.6	1.3		13000	0.49	3.1	11500	43	24	10	0.01	71	3.2	19.5	35	0.73
KL42-09	524.6	527.6	1		10000	0.42	4	540	90	38	15	1	31	7	18.0	54	0.01
KL42-09	527.6	530.6	1.5		15000	0.67	4.1	126	13	9	2	5	31	4.5	12.5	28	0.46
KL42-09	530.6	533.6	1.89		18900	1.88	2.8	137	14	1	4	4	21	0.9	15.5	45	0.1
KL42-09	533.6	536.2	1.58		15800	0.87	1.9	1250	16	18	4	1	26	0.01	11.5	45	0.01
KL42-09	536.2	539.6	0.56		5600	0.16	0.9	57	28	7	19	0.01	7	0.7	5.3	60	0.01
KL42-09	539.6	541.9	0.248		2480	0.19	0.7	53	15	3	26	0.01	8	0.2	2.3	70	0.01
KL42-09	541.9	545.3	0.269		2690	0.21	1.5	480	257	12	18	0.01	10	0.9	3.2	66	0.01
KL42-09	545.3	548.1	0.128		1280	0.11	0.5	62	30	10	22	0.01	8	0.8	2.3	94	0.01
KL42-09	548.1	551.9	1.02		10200	0.76	1.1	1070	41	19	10	0.01	20	0.4	7.2	62	0.01
KL42-09	551.9	554.6	0.44		4400	0.19	2.8	920	560	17	13	0.01	10	1.3	7.0	71	0.01
KL42-09	554.6	557.6	0.129		1290	0.12	0.6	67	37	12	24	0.01	7	0.9	2.0	93	0.01
KL42-09	557.6	560.6	0.92		9200	0.44	11.7	820	1900	21	93	6	10	17.5	12.0	80	0.01
KL42-09	560.6	563.6	0.124		1240	0.18	0.6	134	81	4	5	0.01	5	0.3	1.1	86	0.01
KL42-09	563.6	566.6	0.23		2300	0.28	0.8	245	160	10	12	1	6	0.7	2.0	85	0.01
KL42-09	566.6	569.6	0.23		2300	0.18	0.7	80	23	6	5	0.01	5	0.3	1.9	60	0.01
KL42-09	569.6	572.6	0.24		2400	0.22	3.1	246	570	13	18	3	5	2.1	3.1	65	0.01
KL42-09	572.6	575.6	0.341		3410	0.26	1.6	367	311	12	29	0.01	8	1	2.6	76	0.01
KL42-09	575.6	578.6	0.21		2100	0.21	1.6	267	99	10	18	1	6	1.6	3.0	62	0.01
KL42-09	578.6	581.7	0.191		1910	0.17	1.7	440	148	11	21	2	5	1.5	2.7	102	0.01
KL42-09	581.7	584.7	0.22		2200	0.13	1	173	82	30	20	2	6	2.6	2.1	117	0.01
KL42-09	584.7	587.6	0.33		3300	0.23	1.4	230	30	20	25	2	9	2.7	6.8	26	0.01
KL42-09	587.6	590.6	0.28		2800	0.24	1.5	700	292	17	9	1	7	1.4	2.4	98	0.01
KL42-09	590.6	593.6	0.53		5300	0.34	4.2	1070	190	15	24	1	10	3.5	9.8	68	0.01
KL42-09	593.6	596.6	0.204		2040	0.07	1.5	257	131	5	63	1	5	1.3	1.6	113	0.01
KL42-09	596.6	599.6	0.209		2090	0.08	1.6	247	146	48	42	3	6	5	0.9	150	0.01
KL42-09	599.6	602.6	0.152		1520	0.01	2.2	183	106	75	13	4	7	10	1.8	106	0.01
KL42-09	602.6	605.6	0.381		3810	0.21	1.8	263	62	43	23	3	12	6.7	5.2	65	0.01
KL42-09	605.6	607.8	0.21		2100	0.03	1	115	39	150	5	5	8	13.5	2.9	91	0.01
KL42-09	607.8	611.3	0.15		1500	0.12	1.3	53	30	4	36	5	5	1.5	1.9	142	0.01
KL42-09	611.3	614.6	0.042		420	0.04	0.01	34	13	45	54	2	8	2.7	15.8	167	0.01
KL42-09	614.6	617.6	0.048		480	0.03	0.01	26	8	40	24	1	7	7.6	7.0	215	0.01
KL42-09	617.6	620.6	0.053		530	0.05	0.01	44	22	37	31	2	7	5.9	3.4	310	0.01
KL42-09	620.6	623.6	0.089		890	0.05	0.01	18	11	2	25	3	5	1.4	2.2	167	0.01
KL42-09	623.6	626.2	0.084		840	0.03	0.01	16	6	5	26	2	6	1.3	2.2	123	0.01
KL42-09	626.2	629.3	0.11		1100	0.02	0.6	33	16	2	24	1	6	0.5	1.5	112	0.01
KL42-09	629.3	632.4	0.176		1760	0.03	0.8	96	26	120	8	4	8	12	1.8	111	0.01
KL42-09	632.4	635.5	0.011		110	0.01	0.01	16	6	11	31	2	6	1.7	8.1	145	0.01
KL42-09	635.5	638.6	0.0197		197	0.02	0.01	58	25	14	372	0.01	3	2.4	3.3	142	0.01
KL42-09	638.6	641.6	0.0146		146	0.03	0.01	17	6	16	480	1	6	2.5	4.8	241	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL42-09	641.6	644.6	0.136	1360	0.13	0.6	40	15	10	62	6	5	2.7	2.4	89	0.01
KL42-09	644.6	647.5	0.056	560	0.1	0.01	21	8	83	37	1	8	14.4	2.2	150	0.01
KL42-09	647.5	650.6	0.086	860	0.04	0.9	21	9	2	28	2	6	0.6	1.5	121	0.01
KL42-09	650.6	653.6	0.0338	338	0.09	0.01	18	8	28	24	2	17	3.5	4.8	118	0.01
KL42-09	653.6	656.6	0.0297	297	0.01	0.01	13	8	8	13	1	14	0.9	5.2	110	0.01
KL42-09	656.6	659.6	0.0201	201	0.04	0.01	23	10	8	77	0.01	8	1.7	2.7	146	0.01
KL42-09	659.6	662.6	0.0137	137	0.02	0.01	31	9	7	16	1	5	1.1	3.6	200	0.01
KL42-09	662.6	664.9	0.0192	192	0.03	0.01	12	6	26	31	1	6	3.7	3.9	172	0.01
KL42-09	664.9	668.6	0.069	690	0.03	0.01	13	6	12	11	1	5	1.3	1.4	224	0.01
KL42-09	668.6	671.6	0.071	710	0.01	0.01	56	35	3	31	0.01	3	2.5	1.2	138	0.01
KL42-09	671.6	674.6	0.072	720	0.03	0.01	13	6	12	14	1	5	1.1	1.6	232	0.01
KL42-09	674.6	677.6	0.075	750	0.03	0.01	10	7	150	28	1	6	12.3	2.6	198	0.01
KL42-09	677.6	680.6	0.099	990	0.01	0.7	33	25	4	26	2	2	1	1.6	115	0.01
KL42-09	680.6	683.6	0.101	1010	0.03	0.5	11	6	7	40	2	3	3.7	2.5	70	0.01
KL42-09	683.6	686.6	0.0334	334	0.02	0.01	9	5	11	57	0.01	0.01	2.2	2.0	90	0.01
KL42-09	686.6	689.6	0.0148	148	0.01	0.01	11	0.01	24	40	0.01	4	2.6	5.0	135	0.01
KL42-09	689.6	692.6	0.0361	361	0.01	0.01	14	0.01	13	41	0.01	2	2.3	1.6	114	0.01
KL42-09	692.6	694.8	0.0201	201	0.01	0.01	16	5	3	40	0.01	0.01	1.6	1.2	59	0.01
KL42-09	694.8	697.4	0.041	410	0.01	0.01	25	11	8	56	1	2	1.8	1.4	95	0.01
KL42-09	697.4	700	0.0273	273	0.01	0.01	27	9	4	84	0.01	3	1.4	3.2	91	0.01
KL42-09	700	703	0.415	4150	0.05	0.5	40	19	14	32	0.01	4	0.4	6.0	174	0.01
KL42-09	703	707.5	0.0349	349	0.01	0.01	13	0.01	9	42	0.01	2	2.5	1.9	91	0.01
KL42-09	707.5	710.4	0.0265	265	0.01	0.01	12	0.01	45	25	0.01	2	5.8	1.5	90	0.01
KL42-09	710.4	713.6	0.0329	329	0.01	0.01	40	16	48	33	0.01	0.01	6.4	0.5	87	0.01
KL42-09	713.6	716.3	0.0135	135	0.01	0.01	11	0.01	5	64	0.01	2	0.5	0.5	188	0.01
KL42-09	716.3	719.6	0.0352	352	0.01	0.01	14	6	75	24	0.01	3	8.7	2.7	68	0.01
KL42-09	719.6	722.6	0.01	100	0.01	0.01	14	6	13	44	0.01	2	1.4	1.7	116	0.01
KL42-09	722.6	725.6	0.0206	206	0.01	0.01	23	11	34	34	0.01	2	3	2.9	156	0.01
KL42-09	725.6	728.2	0.0249	249	0.01	0.01	14	7	46	26	0.01	0.01	4.1	2.0	102	0.01
KL42-09	728.2	731.6	0.0239	239	0.01	0.01	21	13	34	25	0.01	0.01	4	2.1	204	0.01
KL42-09	731.6	734.6	0.059	590	0.01	0.01	20	11	150	23	1	3	13	2.6	110	0.01
KL42-09	734.6	737.6	0.0228	228	0.01	0.01	68	21	56	137	0.01	0.01	3.7	2.1	221	0.01
KL42-09	737.6	740.6	0.069	690	0.01	0.01	30	9	47	31	1	2	2.2	4.6	201	0.01
KL42-09	740.6	743.6	0.0299	299	0.01	0.01	12	6	21	30	1	5	2.7	4.1	121	0.01
KL42-09	743.6	746.6	0.0153	153	0.01	0.01	20	8	12	79	0.01	3	1.8	5.0	191	0.01
KL42-09	746.6	749	0.044	440	0.01	0.01	18	8	20	32	0.01	4	1.8	2.6	242	0.01
KL42-09	749	752.1	0.0311	311	0.01	0.01	21	9	36	63	0.01	0.01	3	4.3	200	0.01
KL42-09	752.1	755.2	0.0319	319	0.01	0.01	20	28	7	43	2	0.01	0.8	1.8	59	0.01
KL42-09	755.2	758.3	0.048	480	0.01	0.01	34	21	4	24	1	2	0.4	1.2	313	0.01
KL42-09	758.3	761.3	0.0273	273	0.02	0.01	28	15	71	51	0.01	0.01	4.9	2.3	197	0.01
KL42-09	761.3	764.4	0.0261	261	0.01	0.01	22	16	38	41	1	2	2.9	3.5	160	0.01
KL42-09	764.4	767.5	0.0298	298	0.01	0.01	13	7	1	66	1	0.01	0.3	1.2	103	0.01
KL42-09	767.5	769.7	0.031	310	0.01	0.01	29	10	2	47	0.01	3	0.7	2.4	231	0.01
KL42-09	769.7	772.8	0.045	450	0.01	0.01	30	14	9	54	1	3	0.9	2.6	234	0.01
KL42-09	772.8	774.6	0.0165	165	0.01	0.01	32	18	7	54	0.01	3	0.6	1.9	260	0.01
KL42-09	774.6	776.6	0.0404	404	0.02	0.01	29	9	17	57	0.01	0.01	0.7	3.3	164	0.01
KL42-09	776.6	779.6	0.0363	363	0.01	0.01	24	7	7	41	0.01	0.01	0.7	2.6	208	0.01
KL42-09	779.6	782.6	0.0371	371	0.01	0.01	43	17	7	28	0.01	0.01	0.3	2.5	223	0.01
KL42-09	782.6	785.6	0.067	670	0.01	0.01	81	32	36	33	0.01	0.01	2.6	2.1	288	0.01
KL42-09	785.6	788.6	0.044	440	0.01	0.01	54	14	5	42	0.01	3	1	1.5	121	0.01
KL42-09	788.6	791.6	0.043	430	0.01	0.01	52	22	9	36	1	2	0.8	2.2	193	0.01
KL42-09	791.6	794.6	0.0296	296	0.02	0.01	52	30	39	206	0.01	4	2.3	3.5	305	0.01
KL42-09	794.6	797.6	0.099	990	0.01	0.01	35	16	16	55	1	2	1.8	3.2	170	0.01
KL42-09	797.6	800.6	0.0135	135	0.01	0.01	31	16	13	142	0.01	2	1.4	2.7	243	0.01
KL42-09	800.6	803.6	0.079	790	0.01	0.01	58	21	30	84	1	3	1.9	3.8	108	0.01
KL42-09	803.6	806.6	0.08	800	0.01	0.01	47	19	52	79	1	2	2.4	3.1	177	0.01
KL42-09	806.6	809.6	0.0206	206	0.01	0.01	42	14	23	65	1	2	1.5	3.3	167	0.01
KL42-09	809.6	812.6	0.082	820	0.01	0.01	47	17	21	94	1	2	2.1	3.7	106	0.01
KL42-09	812.6	815.6	0.104	1040	0.01	0.6	26	12	7	82	0.01	0.01	1.1	1.9	118	0.01
KL42-09	815.6	818.6	0.099	990	0.01	0.6	54	20	26	110	0.01	2	1.9	3.3	118	0.01
KL42-09	818.6	820.6	0.107	1070	0.01	0.01	56	29	80	92	1	4	4	3.3	181	0.01
KL42-10	0	2	0.0012	12	0.01	0.01	88	74	9	2	0.01	0.01	1.6	0.8	15	0.12
KL42-10	2	4.7	0.001	10	0.01	0.5	117	67	10	2	0.01	0.01	1.9	0.8	15	0.15

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL42-10	4.7	7.7	0.0019		19	0.01	0.6	167	90	6	0.01	0.01	0.01	1	0.5	14	0.01
KL42-10	7.7	10.7	0.0013		13	0.04	0.5	112	58	14	2	0.01	0.01	1.8	0.6	14	0.01
KL42-10	10.7	13.1	0.0033		33	0.06	1.1	116	148	12	4	0.01	0.01	2.1	0.6	15	0.01
KL42-10	13.1	16.1	0.0015		15	0.03	0.6	117	66	10	3	0.01	0.01	1.8	0.7	15	0.01
KL42-10	16.1	17.1	0.0013		13	0.02	0.01	92	57	9	3	0.01	0.01	1.6	0.6	13	0.01
KL42-10	17.1	19.7	0.0019		19	0.05	0.6	140	58	10	4	0.01	0.01	1.5	1.1	12	0.01
KL42-10	19.7	22.7	0.0031		31	0.17	11.7	7000	3620	65	8	5	0.01	12	29.3	25	0.13
KL42-10	22.7	25.7	0.0008		8	0.15	0.9	153	62	12	3	0.01	0.01	2.1	0.7	23	0.11
KL42-10	25.7	28.7	0.0008		8	0.01	0.01	59	25	7	2	0.01	0.01	1.3	0.0	13	0.01
KL42-10	28.7	31.4	0.001		10	0.04	0.01	97	29	12	3	0.01	0.01	1.8	0.5	18	0.11
KL42-10	31.4	34.5	0.0011		11	0.02	0.01	64	13	8	0.01	0.01	0.01	1.8	0.0	14	0.01
KL42-10	34.5	37.7	0.0009		9	0.02	0.01	137	52	4	2	0.01	0.01	1	0.0	16	0.01
KL42-10	37.7	40.7	0.0006		6	0.05	0.01	134	17	10	0.01	0.01	0.01	2.1	1.3	13	0.27
KL42-10	40.7	43.7	0.0018		18	0.04	0.01	112	29	9	2	0.01	0.01	1.9	1.7	13	0.26
KL42-10	43.7	46.7	0.0007		7	0.03	0.01	95	25	8	0.01	0.01	0.01	2	0.5	13	0.23
KL42-10	46.7	49.7	0.0007		7	0.03	0.6	101	11	8	0.01	0.01	0.01	1.3	0.8	13	0.12
KL42-10	49.7	52.7	0.0008		8	0.02	1.3	243	62	19	2	0.01	0.01	3	1.1	16	0.39
KL42-10	52.7	55.4	0.0012		12	0.04	3.4	460	289	29	3	0.01	0.01	6.1	3.7	15	0.46
KL42-10	55.4	56.7	0.0009		9	0.08	0.8	108	24	10	2	0.01	0.01	2	0.0	15	0.39
KL42-10	56.7	58.7	0.0012		12	0.07	1.2	165	49	18	2	0.01	0.01	2.2	1.2	13	0.36
KL42-10	58.7	61.6	0.0005		5	0.05	0.7	167	36	7	3	0.01	0.01	1.8	0.0	13	0.23
KL42-10	61.6	64.4	0.0008		8	0.04	0.6	98	28	5	0.01	0.01	0.01	1.3	0.6	14	0.24
KL42-10	64.4	67.4	0.0012		12	0.05	0.8	149	35	8	0.01	0.01	0.01	1.4	1.3	16	0.22
KL42-10	67.4	70.3	0.0029		29	0.5	39	760	279	41	3	0.01	0.01	6.1	4.0	32	0.36
KL42-10	70.3	73.2	0.0008		8	0.07	1.2	107	37	8	0.01	0.01	0.01	1.6	1.2	16	0.1
KL42-10	73.2	75	0.0012		12	0.05	2.1	357	136	9	2	0.01	0.01	1.3	3.1	18	0.2
KL42-10	75	76.7	0.0007		7	0.01	0.01	95	36	8	2	0.01	0.01	1.3	1.0	15	0.01
KL42-10	76.7	79.7	0.0023		23	0.04	0.8	253	78	7	0.01	0.01	0.01	1.5	1.3	15	0.12
KL42-10	79.7	82.7	0.0295		295	0.06	1.3	376	111	9	2	0.01	0.01	1.8	1.2	17	0.16
KL42-10	82.7	85.3	0.0179		179	0.11	2.5	840	247	19	3	0.01	0.01	2	1.9	17	0.26
KL42-10	85.3	86.9	0.003		30	0.04	1	206	67	12	2	0.01	0.01	1.5	1.0	21	0.12
KL42-10	86.9	90	0.001		10	0.02	0.5	135	42	5	0.01	0.01	0.01	0.4	0.0	16	0.01
KL42-10	90	91.7	0.0011		11	0.01	0.01	113	43	3	0.01	0.01	0.01	0.5	0.6	18	0.01
KL42-10	91.7	94.7	0.0026		26	0.01	0.01	171	37	3	0.01	0.01	0.01	0.9	0.5	18	0.01
KL42-10	94.7	97.7	0.0018		18	0.01	0.01	87	30	4	4	0.01	0.01	1.3	0.5	20	0.01
KL42-10	97.7	100.7	0.0006		6	0.04	1	219	48	9	2	0.01	0.01	1.9	0.0	36	0.1
KL42-10	100.7	103	0.0007		7	0.06	0.9	287	61	10	0.01	0.01	0.01	2.1	0.6	18	0.1
KL42-10	103	106	0.0238		238	0.17	1	259	44	18	4	0.01	0.01	3	1.5	26	0.01
KL42-10	106	108	0.0016		16	0.04	0.5	185	51	7	3	0.01	0.01	1.3	0.6	17	0.01
KL42-10	108	109.7	0.0008		8	0.03	0.5	260	41	9	2	0.01	0.01	1.1	0.0	13	0.01
KL42-10	109.7	112.7	0.001		10	0.02	0.6	141	35	6	3	0.01	0.01	1.2	0.7	14	0.01
KL42-10	112.7	115.7	0.0013		13	0.01	0.6	192	56	4	3	0.01	0.01	1.1	0.6	13	0.01
KL42-10	115.7	118.6	0.0007		7	0.02	0.6	160	39	4	0.01	0.01	0.01	1	0.5	11	0.01
KL42-10	118.6	121.7	0.0017		17	0.04	1.2	520	110	9	0.01	0.01	0.01	2.1	2.1	13	0.11
KL42-10	121.7	124.7	0.0008		8	0.04	1.4	520	140	9	0.01	0.01	0.01	1.9	1.4	12	0.1
KL42-10	124.7	127.4	0.0009		9	0.02	0.8	181	49	5	0.01	0.01	0.01	1.8	0.9	14	0.01
KL42-10	127.4	129.4	0.0006		6	0.02	1.7	490	181	9	0.01	0.01	0.01	3.3	1.1	23	0.01
KL42-10	129.4	131.6	0.0005		5	0.01	0.7	150	41	9	0.01	0.01	0.01	3	0.7	15	0.01
KL42-10	131.6	133.4	0.0012		12	0.01	0.6	200	62	6	0.01	0.01	0.01	2.2	0.6	11	0.01
KL42-10	133.4	135.2	0.0009		9	0.08	3.2	590	286	35	3	5	0.01	17.8	14.0	23	0.01
KL42-10	135.2	136.7	0.0006		6	0.01	0.8	89	48	10	0.01	0.01	0.01	1.9	2.9	15	0.01
KL42-10	136.7	139.7	0.0013		13	0.01	0.7	213	35	10	0.01	0.01	0.01	1.6	1.4	12	0.01
KL42-10	139.7	142.7	0.0008		8	0.01	0.01	160	36	4	0.01	0.01	0.01	1.1	0.8	17	0.01
KL42-10	142.7	145.7	0.0007		7	0.02	0.01	237	55	7	0.01	0.01	0.01	1.5	0.8	15	0.01
KL42-10	145.7	148.7	0.0006		6	0.01	0.01	218	49	4	0.01	0.01	0.01	0.8	0.6	13	0.01
KL42-10	148.7	150.3	0.0009		9	0.01	0.01	260	58	5	0.01	0.01	0.01	1.1	0.5	11	0.01
KL42-10	150.3	151.7	0.0011		11	0.01	0.01	108	43	5	3	0.01	0.01	1	0.0	13	0.01
KL42-10	151.7	154.7	0.0008		8	0.01	0.01	136	79	2	0.01	0.01	0.01	0.7	0.0	15	0.01
KL42-10	154.7	157.7	0.0012		12	0.01	2.9	3550	450	13	3	0.01	0.01	3.9	3.8	44	0.48
KL42-10	157.7	160.7	0.0009		9	0.01	0.9	286	70	5	0.01	0.01	0.01	1.2	1.0	14	0.01
KL42-10	160.7	163.5	0.0007		7	0.01	0.01	99	38	4	2	0.01	0.01	0.5	0.6	12	0.01
KL42-10	163.5	166.7	0.0006		6	0.01	0.5	187	54	7	0.01	0.01	0.01	1.9	1.0	20	0.01
KL42-10	166.7	169.7	0.0004		4	0.01	0.01	98	31	3	0.01	0.01	0.01	0.5	0.5	20	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL42-10	169.7	172.7	0.0029		29	0.02	0.01	139	39	6	2	0.01	0.01	0.9	0.0	23	0.01
KL42-10	172.7	175.7	0.0013		13	0.01	0.01	178	61	4	2	0.01	0.01	0.7	0.0	18	0.01
KL42-10	175.7	178.7	0.0005		5	0.01	0.01	226	75	2	0.01	0.01	0.01	0.3	0.0	12	0.01
KL42-10	178.7	181.3	0.0004		4	0.01	0.01	148	69	2	0.01	0.01	0.01	0.2	0.0	15	0.01
KL42-10	181.3	184.1	0.0011		11	0.01	0.5	213	106	7	2	0.01	0.01	0.7	0.6	11	0.01
KL42-10	184.1	187.2	0.0007		7	0.01	0.01	186	59	3	0.01	0.01	0.01	0.01	0.0	12	0.01
KL42-10	187.2	190.3	0.0009		9	0.01	1.1	1190	530	8	2	0.01	0.01	0.9	0.7	13	0.01
KL42-10	190.3	192	0.0029		29	0.02	1.6	1560	460	12	5	1	0.01	1.5	1.3	11	0.01
KL42-10	192	193.7	0.0037		37	0.25	14.9	1460	2200	64	10	32	0.01	4.2	16.3	17	0.01
KL42-10	193.7	196.3	0.0012		12	0.01	0.6	356	130	5	0.01	0.01	0.01	0.8	0.7	12	0.01
KL42-10	196.3	199.2	0.0027		27	0.26	13.9	1310	2350	63	6	33	0.01	4.1	13.2	20	0.01
KL42-10	199.2	201.6	0.0021		21	0.02	1.3	520	216	7	4	0.01	0.01	0.5	1.1	14	0.01
KL42-10	201.6	204.1	0.0354		354	0.04	2	339	1270	10	102	0.01	0.01	1.6	1.8	35	0.01
KL42-10	204.1	205.7	0.0015		15	0.07	1.1	620	365	10	2	0.01	0.01	1	1.0	16	0.01
KL42-10	205.7	207.7	0.0137		137	0.03	1.2	377	1010	6	82	0.01	0.01	1.5	1.4	26	0.01
KL42-10	207.7	210.2	0.002		20	0.01	0.8	680	194	8	2	1	0.01	0.7	1.2	10	0.01
KL42-10	210.2	211.7	0.0011		11	0.01	0.7	272	120	7	2	0.01	0.01	0.5	1.2	11	0.01
KL42-10	211.7	214.7	0.0012		12	0.02	0.7	500	155	5	0.01	0.01	0.01	0.7	1.0	13	0.01
KL42-10	214.7	217.7	0.0013		13	0.07	1.2	570	500	8	0.01	0.01	0.01	1.3	1.6	17	0.01
KL42-10	217.7	220.7	0.0016		16	0.09	2.6	980	520	12	3	0.01	0.01	2	2.4	13	0.01
KL42-10	220.7	222.6	0.0016		16	0.08	2.7	1030	490	13	3	0.01	0.01	2.2	2.4	11	0.01
KL42-10	222.6	225.1	0.0021		21	0.07	1.8	1360	780	19	3	0.01	0.01	2.8	2.2	11	0.01
KL42-10	225.1	226.7	0.0063		63	0.07	1.8	930	620	20	4	1	0.01	2.1	2.4	9	0.01
KL42-10	226.7	229.4	0.011		110	0.18	5.3	2050	1520	68	5	2	0.01	7	5.2	14	0.01
KL42-10	229.4	231.6	0.002		20	0.19	1.9	1020	670	19	3	0.01	0.01	2.1	1.9	15	0.01
KL42-10	231.6	232.7	0.0024		24	0.17	2.1	1150	830	15	3	0.01	0.01	1.9	2.0	13	0.01
KL42-10	232.7	235.7	0.001		10	0.05	1.6	860	600	11	2	0.01	0.01	2.6	1.0	11	0.01
KL42-10	235.7	238.7	0.0015		15	0.1	1	510	272	6	0.01	0.01	0.01	0.8	3.2	18	0.01
KL42-10	238.7	240.7	0.0011		11	0.05	1	540	367	11	2	0.01	0.01	1.3	1.7	17	0.01
KL42-10	240.7	243.9	0.0018		18	0.04	1	610	430	10	0.01	0.01	0.01	1.6	2.0	15	0.01
KL42-10	243.9	246.8	0.0014		14	0.12	1.3	720	374	12	0.01	0.01	0.01	2.8	1.7	21	0.01
KL42-10	246.8	249.8	0.0011		11	0.02	3.2	1350	1130	13	0.01	0.01	0.01	4	1.5	9	0.01
KL42-10	249.8	250.7	0.0012		12	0.01	0.6	670	251	6	0.01	0.01	0.01	0.9	0.0	12	0.01
KL42-10	250.7	253.7	0.0042		42	0.17	7.6	4800	4070	59	0.01	1	0.01	11.5	4.6	17	0.11
KL42-10	253.7	256.3	0.0023		23	0.17	2.7	2170	860	23	2	0.01	0.01	3.9	5.2	16	0.1
KL42-10	256.3	259.4	0.0009		9	0.08	1.2	900	560	7	0.01	0.01	0.01	1.3	2.6	17	0.01
KL42-10	259.4	262.4	0.0015		15	0.1	1.5	800	610	7	0.01	0.01	0.01	1.5	3.0	15	0.01
KL42-10	262.4	265.5	0.0015		15	0.07	1.4	800	580	8	0.01	0.01	0.01	1.4	2.7	20	0.01
KL42-10	265.5	268.6	0.0008		8	0.08	1.2	640	325	5	0.01	0.01	0.01	0.9	2.1	18	0.01
KL42-10	268.6	271.7	0.0036		36	0.15	2.1	1900	990	15	0.01	0.01	0.01	2	2.3	20	0.01
KL42-10	271.7	273.7	0.002		20	0.14	2.3	1070	800	13	0.01	0.01	0.01	2.5	3.6	15	0.01
KL42-10	273.7	275.7	0.74		7400	0.32	6.2	1490	780	200	5	11	0.01	9	4.3	54	0.11
KL42-10	275.7	277.6	0.0041		41	0.27	1.2	830	400	13	0.01	0.01	0.01	2	2.0	28	0.01
KL42-10	277.6	280.6	0.0088		88	0.14	0.9	750	580	10	0.01	0.01	3	1.3	1.5	21	0.01
KL42-10	280.6	283.7	0.033		330	0.08	1	680	600	19	0.01	3	2	1.3	2.6	18	0.01
KL42-10	283.7	285.2	0.0114		114	0.08	1.3	1640	1010	36	2	0.01	0.01	2.1	7.9	16	0.01
KL42-10	285.2	286.7	0.0169		169	0.13	2.2	3580	1860	50	0.01	0.01	2	4	10.8	24	0.13
KL42-10	286.7	289.8	0.0297		297	0.15	3.4	2780	3240	79	0.01	1	0.01	4.3	13.0	20	0.2
KL42-10	289.8	292.7	0.175		1750	0.24	13.6	9500	7900	420	3	16	2	7.5	46.5	25	1.33
KL42-10	292.7	295	5		50000	0.4	67	3200	1510	2870	23	197	0.01	32	10.0	115	0.72
KL42-10	295	296.3	1.3		13000	0.12	8.8	1960	810	2300	7	14	0.01	8.8	5.0	21	0.31
KL42-10	296.3	299.4	0.0241		241	0.28	1.5	6700	1150	50	4	1	0.01	3	8.4	19	0.12
KL42-10	299.4	301.6	0.0205		205	0.28	3.9	2750	2100	55	6	6	0.01	2.6	13.0	18	0.18
KL42-10	301.6	303	0.0296		296	0.41	8.1	9900	6300	100	31	8	0.01	6.4	29.2	21	0.15
KL42-10	303	306	0.006		60	0.05	4.1	1240	2250	19	0.01	0.01	0.01	4.6	3.8	11	0.01
KL42-10	306	308.9	0.0097		97	0.07	46	23300	40500	27	4	0.01	0.01	40	15.5	17	0.13
KL42-10	308.9	311.9	0.0018		18	0.04	0.9	560	510	11	3	0.01	0.01	0.8	1.2	17	0.01
KL42-10	311.9	314.8	0.0078		78	0.06	3.4	2820	2330	35	4	1	0.01	4.4	5.4	13	0.01
KL42-10	314.8	318	0.0023		23	0.08	0.8	1070	560	6	0.01	0.01	0.01	1	1.4	17	0.01
KL42-10	318	319.7	0.011		110	0.05	11.2	7500	7000	21	2	1	0.01	13.1	4.0	14	0.1
KL42-10	319.7	321.2	0.0041		41	0.03	1	560	800	10	3	1	0.01	1.5	1.8	18	0.01
KL42-10	321.2	322.7	0.0023		23	0.04	1.2	630	900	10	0.01	0.01	0.01	1.7	1.1	17	0.01
KL42-10	322.7	324.2	0.0039		39	0.04	1	520	800	9	2	2	0.01	0.9	2.5	17	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL42-10	324.2	326	0.0031		31	0.03	2.2	660	1050	10	4	3	0.01	1.4	3.0	16	0.01
KL42-10	326	328.7	0.0033		33	0.02	0.9	420	610	7	0.01	0.01	2	1.7	2.0	15	0.01
KL42-10	328.7	330.7	0.0035		35	0.03	0.8	790	420	11	0.01	0.01	0.01	1.2	1.5	13	0.01
KL42-10	330.7	333.5	0.0028		28	0.03	0.01	430	208	7	0.01	0.01	3	0.6	1.0	16	0.01
KL42-10	333.5	334.8	0.0032		32	0.04	0.9	910	500	10	2	0.01	0.01	1.2	2.5	11	0.01
KL42-10	334.8	337.4	0.0055		55	0.04	0.9	730	610	6	2	0.01	0.01	1.4	1.3	13	0.01
KL42-10	337.4	340.7	0.0187		187	0.21	0.8	770	355	12	7	0.01	0.01	1.2	2.1	21	0.01
KL42-10	340.7	343.8	0.0055		55	0.03	0.01	388	300	6	3	0.01	0.01	0.8	0.8	20	0.01
KL42-10	343.8	346.8	0.0062		62	0.04	2.6	4760	2300	12	8	2	0.01	2.8	3.8	17	0.01
KL42-10	346.8	349.1	0.015		150	0.05	39	65000	58600	25	4	0.01	0.01	50	8.5	16	0.1
KL42-10	349.1	352.2	0.0079		79	0.07	6.7	3210	6500	23	11	9	0.01	5.5	5.0	18	0.01
KL42-10	352.2	353.9	0.0036		36	0.04	1	450	325	10	2	0.01	0.01	1	1.3	18	0.01
KL42-10	353.9	355.8	0.0022		22	0.03	9.8	1340	7000	11	4	0.01	2	12.4	2.6	12	0.01
KL42-10	355.8	358.8	0.0031		31	0.08	89	2800	40000	24	6	2	2	112	10.3	14	0.12
KL42-10	358.8	361.8	0.0019		19	0.02	8.9	470	6700	8	2	0.01	0.01	14.4	1.0	14	0.01
KL42-10	361.8	364.8	0.0018		18	0.01	1.5	251	450	7	2	0.01	0.01	1.4	0.0	18	0.01
KL42-10	364.8	367.8	0.0144		144	0.09	1.4	1280	580	70	7	2	0.01	4.3	6.3	17	0.1
KL42-10	367.8	370.7	0.004		40	0.07	0.9	1100	750	11	4	0.01	0.01	1.3	4.0	15	0.01
KL42-10	370.7	373.5	0.0054		54	0.06	5	1060	2300	31	4	1	0.01	7.1	3.8	16	0.01
KL42-10	373.5	376.2	0.0026		26	0.02	0.6	460	330	10	4	0.01	0.01	1.2	1.5	20	0.01
KL42-10	376.2	377.3	0.0031		31	0.02	0.01	258	85	9	2	0.01	0.01	0.6	1.0	21	0.01
KL42-10	377.3	379.1	0.0021		21	0.02	0.01	232	105	6	2	0.01	0.01	0.8	1.1	17	0.01
KL42-10	379.1	381.7	0.002		20	0.02	0.01	225	117	6	3	0.01	0.01	0.8	1.3	15	0.01
KL42-10	381.7	383.6	0.0052		52	0.05	0.7	870	420	12	2	0.01	0.01	1.8	3.0	22	0.01
KL42-10	383.6	385.2	0.0128		128	0.03	0.7	220	133	15	5	2	0.01	1.4	2.3	24	0.01
KL42-10	385.2	388.1	0.0135		135	0.04	0.6	242	146	18	6	1	0.01	0.6	2.3	29	0.01
KL42-10	388.1	390.8	0.0097		97	0.02	0.5	184	214	15	5	2	0.01	0.9	2.2	24	0.01
KL42-10	390.8	393.9	0.0117		117	0.02	0.5	100	105	12	5	2	0.01	0.8	2.3	23	0.01
KL42-10	393.9	395.6	0.002		20	0.02	0.01	480	292	6	3	0.01	0.01	0.9	1.7	16	0.01
KL42-10	395.6	397	0.0352		352	0.04	0.6	221	58	11	3	1	0.01	0.8	2.9	26	0.01
KL42-10	397	398.6	0.0104		104	0.02	0.01	121	46	24	8	1	0.01	0.5	2.0	22	0.01
KL42-10	398.6	400.8	0.051		510	0.07	0.5	660	29	23	9	2	3	1.6	3.2	25	0.01
KL42-10	400.8	403.8	0.05		500	0.03	0.01	520	176	17	3	2	0.01	0.8	5.2	26	0.01
KL42-10	403.8	406.8	0.0085		85	0.02	0.01	323	53	15	5	2	0.01	1	2.5	20	0.01
KL42-10	406.8	409.8	0.0137		137	0.07	0.01	238	57	15	16	2	0.01	0.8	4.0	28	0.01
KL42-10	409.8	412.8	0.0132		132	0.04	0.01	248	48	16	6	1	0.01	0.5	3.2	31	0.01
KL42-10	412.8	415.8	0.067		670	0.06	0.7	301	44	38	10	4	3	1.5	5.2	18	0.01
KL42-10	415.8	418.8	0.112		1120	0.1	0.9	540	70	44	18	3	4	2.1	5.0	22	0.01
KL42-10	418.8	421.8	0.058		580	0.07	0.01	690	27	27	7	2	2	1.6	3.0	25	0.01
KL42-10	421.8	424.8	0.054		540	0.11	0.7	680	18	20	11	5	5	1.6	4.8	33	0.01
KL42-10	424.8	427.8	0.089		890	0.14	0.7	830	23	24	89	2	7	0.9	5.3	22	0.01
KL42-10	427.8	430.8	0.365		3650	1.6	2	1830	41	24	58	6	15	1.1	5.4	19	0.01
KL42-10	430.8	433.8	0.139		1390	0.9	1	1000	31	34	27	2	5	1.6	5.8	31	0.01
KL42-10	433.8	436.7	0.055		550	0.34	0.01	650	26	25	9	1	3	0.7	3.5	22	0.01
KL42-10	436.7	439.7	0.121		1210	0.44	0.7	590	110	25	2	3	2	1.2	4.9	16	0.01
KL42-10	439.7	442.7	0.298		2980	0.38	2.3	292	57	120	38	2	3	4	4.3	32	0.01
KL42-10	442.7	445.7	0.115		1150	0.29	0.7	1850	16	65	3	2	10	0.9	7.2	39	0.1
KL42-10	445.7	448.7	0.18		1800	0.28	1.2	1220	39	69	4	2	10	0.7	11.0	38	0.1
KL42-10	448.7	451.7	0.61		6100	0.68	4.5	1430	16	66	8	2	19	1.2	31.3	50	0.4
KL42-10	451.7	454.7	0.295		2950	0.42	1.8	2090	22	51	16	2	13	1.1	17.0	56	0.38
KL42-10	454.7	457.7	0.416		4160	0.42	2.1	460	63	16	38	24	8	0.5	12.5	35	0.01
KL42-10	457.7	460.7	0.76		7600	1.2	3.5	790	14	14	15	2	18	0.3	10.0	34	0.1
KL42-10	460.7	463.7	0.66		6600	1.06	3.9	660	31	38	4	3	13	0.9	14.5	47	0.14
KL42-10	463.7	466.7	0.89		8900	1.15	11	6400	6600	28	12	18	13	0.9	19.0	41	0.59
KL42-10	466.7	469.7	1.12		11200	1.3	1.5	116	19	21	17	1	12	0.4	11.0	129	0.01
KL42-10	469.7	472.7	0.93		9300	0.96	3	2400	780	24	39	4	9	1	18.0	172	0.01
KL42-10	472.7	475.7	0.511		5110	0.47	1.5	283	184	34	59	4	9	1	19.0	80	0.1
KL42-10	475.7	478.7	0.56		5600	0.36	2.9	278	196	100	60	4	6	4	39.5	100	0.14
KL42-10	478.7	481.7	0.108		1080	0.19	2.2	2700	1380	28	17	1	0.01	2.6	10.6	52	0.27
KL42-10	481.7	484.7	0.41		4100	0.42	1.1	296	115	40	25	2	5	1.5	5.8	51	0.01
KL42-10	484.7	487.7	0.52		5200	0.62	1.7	349	213	98	176	3	9	6.3	7.5	120	0.01
KL42-10	487.7	490.7	0.29		2900	0.3	1.9	460	380	32	182	5	8	2.6	10.5	94	0.01
KL42-10	490.7	492.6	0.0067		67	0.08	2.2	1230	850	27	3	1	0.01	3.5	3.3	14	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL42-10	492.6	495.3	0.5	5000	0.48	10.5	1020	5010	56	596	1	10	8.8	8.3	113	0.01
KL42-10	495.3	497.4	0.071	710	0.09	3.5	174	2600	21	271	2	2	3.6	4.0	70	0.01
KL42-10	497.4	499	0.112	1120	0.14	1.6	420	740	23	103	3	4	4.2	5.8	43	0.01
KL42-10	499	501	0.68	6800	0.77	5.6	372	94	260	99	5	7	8.5	7.0	37	0.17
KL42-10	501	502.7	0.94	9400	0.57	5	402	460	1780	101	7	8	100	9.0	213	0.15
KL42-10	502.7	505.7	0.098	980	0.17	19.5	9000	15500	330	7	2	2	49	7.3	67	0.13
KL42-10	505.7	508.7	0.443	4430	0.59	3.1	580	124	750	45	4	9	208	14.8	147	0.36
KL42-10	508.7	511.7	0.58	5800	0.6	3.7	184	158	1670	53	3	11	190	7.5	120	0.17
KL42-10	511.7	514.7	0.28	2800	0.24	2.2	73	191	680	90	3	4	62	6.8	121	0.01
KL42-10	514.7	517.7	0.326	3260	0.46	3	148	79	840	145	3	6	69	10.0	114	0.1
KL42-10	517.7	520.7	0.056	560	0.34	2	48	59	72	39	2	8	17.3	9.3	152	0.01
KL42-10	520.7	523.7	0.48	4800	0.44	28.3	2430	6300	170	73	30	8	32	13.0	157	0.88
KL42-10	523.7	526.7	0.21	2100	0.4	6.8	1030	680	72	277	9	6	45	14.5	139	0.46
KL42-10	526.7	529.8	0.302	3020	0.67	4	4500	4400	170	104	3	6	10.6	14.8	124	0.17
KL42-10	529.8	531.9	0.074	740	0.19	0.01	460	159	20	31	0.01	3	1.1	3.0	63	0.01
KL42-10	531.9	534	0.0337	337	0.39	0.01	1430	149	36	50	1	4	1.2	5.3	59	0.01
KL42-10	534	536.5	0.117	1170	0.37	0.01	219	97	25	51	1	3	1.4	5.8	36	0.01
KL42-10	536.5	538.7	0.0285	285	0.54	0.01	1550	550	43	149	1	4	1.1	6.0	92	0.01
KL42-10	538.7	541.7	0.081	810	1.31	0.6	1920	570	46	174	1	5	4.5	9.5	124	0.01
KL42-10	541.7	543.2	0.61	6100	1.03	1.2	1920	410	52	115	1	8	5.6	11.8	118	0.01
KL42-10	543.2	544.7	0.0215	215	0.2	0.01	100	24	13	4	0.01	18	0.8	1.2	45	0.01
KL42-10	544.7	547.7	0.0221	221	0.17	0.01	100	20	11	17	0.01	21	0.6	1.0	45	0.01
KL42-10	547.7	550.6	0.011	110	0.05	0.01	103	19	7	0.01	0.01	20	0.5	0.6	53	0.01
KL42-10	550.6	553.6	0.024	240	0.12	0.01	130	52	24	0.01	0.01	22	0.4	1.0	50	0.01
KL42-10	553.6	556.7	0.0235	235	0.21	0.01	92	18	29	0.01	0.01	22	0.3	5.0	29	0.01
KL42-10	556.7	559.7	0.008	80	0.1	0.01	114	19	13	0.01	0.01	20	0.2	4.3	30	0.01
KL42-10	559.7	562.7	0.0091	91	0.12	0.01	89	13	25	0.01	0.01	20	0.3	5.0	58	0.01
KL42-10	562.7	565.7	0.0102	102	0.09	0.01	103	12	6	0.01	0.01	21	0.01	1.0	43	0.01
KL42-10	565.7	568.7	0.0099	99	0.09	0.01	86	10	3	0.01	0.01	22	0.01	1.1	30	0.01
KL42-10	568.7	571.7	0.045	450	0.04	0.01	78	14	3	0.01	0.01	22	0.3	1.2	35	0.01
KL42-10	571.7	574.5	0.028	280	0.01	0.01	136	28	50	2	0.01	20	3.1	0.8	54	0.11
KL42-10	574.5	576.1	0.107	1070	0.16	0.5	106	21	10	8	2	21	1.5	2.7	46	0.01
KL42-10	576.1	577.6	1.96	19600	1.98	7.1	420	62	18	25	20	31	5.9	10.5	118	0.01
KL42-10	577.6	580.7	1.25	12500	1.35	4.5	950	43	22	10	13	28	8	13.0	119	0.01
KL42-10	580.7	583.7	1.85	18500	2.32	5.1	156	18	21	12	27	22	7.5	11.5	80	0.01
KL42-10	583.7	586.7	1.54	15400	1.51	2.6	218	16	17	186	5	17	4.8	10.0	82	0.01
KL42-10	586.7	589.7	1.52	15200	1.11	3	106	11	14	17	6	16	2.4	13.5	60	0.01
KL42-10	589.7	592.7	2.38	23800	1.73	3.1	150	8	15	5	1	20	0.9	13.0	59	0.01
KL42-10	592.7	594.2	3.8	38000	1.56	5.7	570	149	25	500	6	18	3.5	36.3	61	0.12
KL42-10	594.2	595.7	0.76	7600	0.62	4.8	1280	840	18	8	5	14	3.6	12.5	99	0.01
KL42-10	595.7	597.4	0.33	3300	0.5	1.8	122	32	8	5	0.01	9	0.7	2.3	89	0.01
KL42-10	597.4	599.7	0.24	2400	0.19	1.1	820	115	7	7	1	3	0.9	4.3	130	0.11
KL42-10	599.7	601.7	0.38	3800	0.32	2.2	2040	142	42	98	5	32	5.7	23.4	59	1.17
KL42-10	601.7	604.3	0.22	2200	0.1	1	213	68	48	320	6	5	7.2	6.5	155	0.1
KL42-10	604.3	607.5	0.139	1390	0.04	0.7	37	13	10	215	5	8	4.4	10.8	135	0.01
KL42-10	607.5	610.4	0.156	1560	0.04	1.2	56	24	17	85	5	5	4.8	3.3	118	0.01
KL42-10	610.4	611.8	0.125	1250	0.04	1.1	71	13	17	37	6	8	4	7.0	105	0.01
KL42-10	611.8	613.7	0.68	6800	0.12	2.9	480	243	30	28	5	5	5	8.5	39	0.01
KL42-10	613.7	614.7	0.36	3600	0.1	1.6	420	137	11	112	4	6	1.3	5.3	112	0.01
KL42-10	614.7	617.7	0.21	2100	0.26	0.7	283	39	56	41	1	7	2.5	4.3	75	0.1
KL42-10	617.7	619.7	0.193	1930	0.82	0.5	117	52	5	6	0.01	5	0.4	1.4	36	0.01
KL42-10	619.7	622.7	0.24	2400	0.51	0.01	62	12	2	3	2	5	0.2	5.5	69	0.01
KL42-10	622.7	625.7	0.54	5400	0.93	0.6	61	15	5	4	0.01	7	0.4	2.0	68	0.01
KL42-10	625.7	628.7	1	10000	0.44	1.9	134	64	15	12	3	6	4.4	12.5	52	0.01
KL42-10	628.7	631.7	3.21	32100	0.78	14.3	1500	65	3300	32	276	28	2110	72.5	38	1.2
KL42-10	631.7	634.7	1.07	10700	0.6	4.2	112	18	260	160	5	19	101	33.0	94	0.28
KL42-10	634.7	637.7	0.199	1990	0.05	1.3	107	29	21	430	3	10	4	10.9	90	0.01
KL42-10	637.7	640.7	0.129	1290	0.05	1	154	52	37	840	4	16	5.3	18.5	232	0.01
KL42-10	640.7	643.7	0.067	670	0.03	0.7	43	16	19	111	2	3	1.3	3.0	171	0.01
KL42-10	643.7	646.7	0.154	1540	0.03	0.8	167	136	5	23	0.01	2	1.4	2.3	48	0.01
KL42-10	646.7	649.7	0.168	1680	0.04	0.6	93	51	30	65	3	3	4	3.8	110	0.01
KL42-10	649.7	652.7	0.21	2100	0.04	0.01	99	41	26	100	0.01	3	1.4	0.8	148	0.01
KL42-10	652.7	655.2	0.21	2100	0.05	1.3	226	80	76	84	1	4	3.8	3.0	169	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL42-10	655.2	656.4	0.52	5200	0.2	12.1	3200	710	1650	83	6	6	78	3.8	185	3.64
KL42-10	656.4	658.7	0.048	480	0.04	0.5	43	19	69	75	1	3	3.7	3.5	148	0.01
KL42-10	658.7	661.7	0.147	1470	0.04	1.1	108	56	70	136	3	6	4.1	4.3	124	0.2
KL42-10	661.7	664.7	0.184	1840	0.05	1.4	139	39	140	61	4	5	18	4.3	80	0.17
KL42-10	664.7	666.5	0.146	1460	0.04	1.1	65	47	30	110	4	9	4.2	10.4	68	0.01
KL42-10	666.5	668	0.193	1930	0.05	0.5	154	243	23	60	0.01	6	2	3.5	167	0.01
KL42-10	668	670.7	0.149	1490	0.01	0.01	98	73	9	37	0.01	3	1.5	2.3	132	0.01
KL42-10	670.7	673.7	0.174	1740	0.01	0.8	176	160	5	51	0.01	5	1.1	1.5	165	0.01
KL42-10	673.7	676.7	0.25	2500	0.08	1	76	80	68	67	2	7	13.7	6.3	87	0.01
KL42-10	676.7	679.7	0.23	2300	0.03	1.4	145	65	30	78	2	9	3	6.0	78	0.01
KL42-10	679.7	682.7	0.22	2200	0.06	1.3	244	75	140	71	2	7	7	4.8	54	0.01
KL42-10	682.7	685.7	0.21	2100	0.05	1.2	264	89	130	76	2	7	7.3	4.8	59	0.01
KL42-10	685.7	688.7	0.21	2100	0.02	1.1	126	91	56	66	2	6	1.7	2.5	66	0.01
KL42-10	688.7	691.7	0.184	1840	0.03	0.9	100	34	29	171	3	7	3.5	7.0	36	0.01
KL42-10	691.7	694.7	0.22	2200	0.03	1.3	168	80	51	81	2	7	4.5	5.5	71	0.01
KL42-10	694.7	697.7	0.362	3620	0.04	1.1	57	32	19	62	2	6	1.5	2.8	29	0.01
KL42-10	697.7	699	0.298	2980	0.03	1.2	76	34	23	82	3	10	1.8	3.0	195	0.01
KL42-10	699	702	0.31	3100	0.04	0.9	60	21	21	85	2	3	1.1	3.3	170	0.01
KL42-10	702	705	0.265	2650	0.04	0.9	83	34	46	209	3	6	10	5.6	214	0.01
KL42-10	705	706.8	0.168	1680	0.05	1.8	93	58	110	312	4	7	14.5	4.3	180	0.13
KL42-10	706.8	709.7	0.096	960	0.03	0.8	67	29	33	258	2	8	5.6	4.5	290	0.1
KL42-10	709.7	710.8	0.156	1560	0.04	1.1	76	37	49	277	3	7	6.2	3.8	242	0.1
KL42-10	710.8	713.3	0.052	520	0.01	0.5	52	26	55	146	1	4	1.8	1.8	281	0.01
KL44-01	0	3	0.0232	232	0.38	2.6	2960	1480	61	70	9	1	3.9	5.5	25	0.54
KL44-01	3	6	0.0041	41	0.01	1.6	76	42	10	5	0.01	1	0.9	1.2	18	0.01
KL44-01	6	9	0.0047	47	0.08	1.1	328	325	26	13	3	1	1	2.3	16	0.01
KL44-01	9	12	0.0036	36	0.01	0.1	53	44	10	3	0.01	1	0.6	0.8	21	0.01
KL44-01	12	15	0.0043	43	0.01	0.5	68	23	7	1	0.01	1	0.6	1.4	17	0.01
KL44-01	15	18	0.0059	59	0.02	1.7	66	28	20	6	0.01	1	0.6	0.9	17	0.01
KL44-01	18	21	0.0055	55	0.01	2.6	83	46	24	6	0.01	1	1.3	1.0	14	0.01
KL44-01	21	24	0.0038	38	0.02	1	69	34	13	3	0.01	1	1.6	1.0	15	0.01
KL44-01	24	27	0.0039	39	0.01	0.5	79	31	13	4	0.01	1	1	1.4	24	0.01
KL44-01	27	30	0.0062	62	0.05	1.2	210	110	22	9	1	2	1	1.8	21	0.01
KL44-01	30	33	0.0014	14	0.03	0.5	64	36	12	2	0.01	1	3.1	0.6	22	0.26
KL44-01	33	36	0.002	20	0.07	0.6	88	44	15	3	0.01	1	3.4	0.5	19	0.43
KL44-01	36	39	0.0044	44	0.05	0.9	92	82	7	5	0.01	1	1.2	0.7	16	0.1
KL44-01	39	42	0.0028	28	0.04	1.4	261	106	8	4	1	2	2.8	1.8	18	0.01
KL44-01	42	45	0.0049	49	0.06	1.7	830	152	14	10	7	1	5.7	2.9	23	0.01
KL44-01	45	48	0.0017	17	0.02	1.2	88	38	10	2	0.01	1	2	1.6	28	0.12
KL44-01	48	51	0.0016	16	0.01	0.7	49	35	9	1	0.01	3	0.7	0.8	20	0.01
KL44-01	51	54	0.0034	34	0.02	1	121	246	16	3	0.01	1	1.4	4.5	26	0.01
KL44-01	54	57	0.0025	25	0.01	1.1	48	50	8	2	0.01	1	0.7	1.0	20	0.01
KL44-01	57	60	0.0045	45	0.01	0.9	47	27	10	7	0.01	1	1.6	1.6	21	0.12
KL44-01	60	63	0.0023	23	0.01	0.1	55	28	15	2	0.01	1	1.1	3.1	24	0.14
KL44-01	63	66	0.0041	41	0.01	1	116	74	12	5	0.01	1	1	2.6	25	0.01
KL44-01	66	69	0.0033	33	0.04	1.5	179	221	26	5	0.01	1	2.6	5.3	22	0.01
KL44-01	69	72	0.0104	104	0.07	2.7	319	680	31	19	3	1	4	9.1	23	0.32
KL44-01	72	75	0.0244	244	0.09	4.8	530	1180	35	45	8	1	4.7	29.5	37	0.34
KL44-01	75	78	0.005	50	0.03	2	420	380	27	9	3	1	2.7	9.6	30	0.01
KL44-01	78	81	0.0038	38	0.02	2.1	240	145	17	3	0.01	1	1.6	7.8	25	0.01
KL44-01	81	84	0.004	40	0.04	1	186	223	22	5	0.01	1	2.5	9.9	27	0.1
KL44-01	84	87	0.0047	47	0.03	0.9	133	268	28	6	0.01	1	2.7	4.4	25	0.22
KL44-01	87	90	0.0053	53	0.02	0.8	118	145	23	5	0.01	1	1.8	2.6	33	0.36
KL44-01	90	93	0.0039	39	0.03	1	170	630	18	3	0.01	1	2.1	7.1	28	0.01
KL44-01	93	96	0.0165	165	0.03	1.4	1280	480	42	11	7	1	2.6	9.4	46	0.01
KL44-01	96	99	0.05	500	0.05	1.4	4530	98	68	23	16	3	3.3	5.2	66	0.1
KL44-01	99	102	0.0095	95	0.08	1.5	980	440	91	254	3	1	5	3.1	43	0.12
KL44-01	102	105	0.11	1100	0.05	2.1	10400	147	60	76	41	7	3.4	13.0	73	0.11
KL44-01	105	108.3	1.59	15900	0.42	22.4	63900	940	1270	1240	490	37	17.1	56.3	69	0.68
KL44-01	108.3	112	0.18	1800	1.46	15.4	43800	1520	470	1330	376	16	17.5	63.0	114	0.4
KL44-01	112	115	0.0238	238	0.12	4.6	2510	1820	82	95	5	1	17	3.5	40	0.24
KL44-01	115	118	0.0173	173	0.24	7	3970	1600	160	820	3	1	11	4.3	35	0.38
KL44-01	118	121	0.0191	191	0.12	2.7	1400	800	49	115	2	2	5.5	2.9	30	0.12

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL44-01	121	124	0.0349		349	0.49	4	3830	630	95	208	8	2	10.7	6.7	35	0.21
KL44-01	124	127	0.069		690	0.63	5.7	7600	730	240	1210	62	4	11.8	13.1	55	0.28
KL44-01	127	130	0.213		2130	0.52	13.6	8930	1730	780	131	164	11	58	25.5	59	1.25
KL44-01	130	133	0.39		3900	0.46	26.1	11900	5500	1260	1650	48	8	149	39.5	91	1.2
KL44-01	133	136	0.069		690	0.31	5.1	4000	860	120	680	29	3	18	8.5	32	0.32
KL44-01	136	139	0.0326		326	0.07	1	1040	105	100	96	2	3	4.8	2.1	18	0.52
KL44-01	139	142	0.03		300	0.07	0.8	1050	101	100	78	1	3	7.3	2.1	21	0.48
KL44-01	142	145	0.35		3500	0.52	4.4	14100	245	900	620	36	17	24	22.0	38	1.36
KL44-01	145	148	0.098		980	0.32	2.1	11000	210	170	210	34	5	10.5	7.8	32	0.5
KL44-01	148	151	0.0204		204	0.07	1.3	1120	127	43	45	27	4	5.6	6.9	23	0.14
KL44-01	151	154	0.117		1170	0.25	1.7	4630	139	270	262	9	7	11.4	7.0	35	0.7
KL44-01	154	157	0.0278		278	0.12	1.4	990	255	100	118	3	1	8.8	4.4	22	0.33
KL44-01	157	160	0.056		560	0.42	4.8	5270	500	140	192	13	2	27	9.6	42	0.22
KL44-01	160	163	0.082		820	0.52	3	9600	277	180	267	15	5	18	10.0	43	0.43
KL44-01	163	166	0.108		1080	0.48	8.1	11900	950	230	728	36	6	25	22.5	41	0.58
KL44-01	166	169	0.164		1640	2.37	20.5	43600	3500	370	401	89	25	67	43.0	75	0.55
KL44-01	169	172	0.0186		186	0.53	3.3	2840	1850	93	189	16	2	6	10.5	33	0.11
KL44-01	172	175	0.0252		252	0.23	3	1880	1730	76	102	7	1	7.2	9.0	26	0.13
KL44-01	175	178	0.0325		325	0.36	3.6	5940	1700	170	188	16	2	7.9	15.3	32	0.3
KL44-01	178	181	0.0309		309	0.44	5.1	6630	2090	200	221	26	1	5.5	21.4	34	0.18
KL44-01	181	184	0.0195		195	0.4	2.5	3320	690	110	170	15	1	3.1	5.9	30	0.14
KL44-01	184	187	0.0369		369	0.65	5	5100	2380	130	150	25	2	10	10.0	31	0.18
KL44-01	187	190	0.044		440	0.38	4.6	4290	1140	140	127	21	2	24	11.4	37	0.2
KL44-01	190	193	0.019		190	0.17	2.4	2230	410	64	99	8	3	3.8	6.3	27	0.11
KL44-01	193	195	0.0121		121	0.18	3.9	2080	1890	38	35	9	1	2.8	9.0	27	0.11
KL44-01	195	197.2	0.0073		73	0.14	2.4	890	940	32	24	7	1	2.2	4.8	18	0.01
KL44-01	197.2	200.2	0.0295		295	0.41	7.4	5300	3560	100	46	27	1	4.1	26.5	34	0.25
KL44-01	200.2	203.4	0.68		6800	1.4	3.9	43600	86	410	368	39	82	5.3	38.5	107	0.44
KL44-01	203.4	205.4	0.09		900	0.28	0.7	3000	29	100	679	6	10	1.8	8.8	20	0.14
KL44-01	205.4	208	0.091		910	0.21	0.6	790	42	100	585	4	6	1.1	4.7	38	0.1
KL44-02	0	3	0.0028		28	0.01	1.8	190	241	16	3	0.01	1	1.8	2.2	30	0.01
KL44-02	3	6	0.0114		114	0.03	0.5	70	53	23	23	0.01	1	1.3	1.0	26	0.01
KL44-02	6	9	0.0025		25	0.01	0.1	44	33	4	1	0.01	1	0.7	0.8	23	0.01
KL44-02	9	12	0.004		40	0.01	0.1	24	10	8	2	0.01	2	0.6	1.5	23	0.01
KL44-02	12	15	0.0062		62	0.02	10.2	640	480	32	3	0.01	1	5.6	7.6	22	0.1
KL44-02	15	18	0.0029		29	0.02	0.1	69	40	21	1	0.01	2	1.6	2.3	21	0.01
KL44-02	18	21	0.0046		46	0.07	1.8	510	281	35	5	2	3	2	3.8	24	0.1
KL44-02	21	24	0.0052		52	0.01	1.4	101	50	14	3	0.01	2	1.2	1.6	28	0.01
KL44-02	24	27	0.0039		39	0.02	0.9	153	40	13	17	0.01	1	2	2.0	24	0.01
KL44-02	27	30	0.0023		23	0.03	1	74	22	10	3	0.01	1	0.6	1.3	20	0.1
KL44-02	30	33	0.003		30	0.08	0.9	63	17	9	3	0.01	1	1.3	2.0	20	0.1
KL44-02	33	36	0.0032		32	0.01	0.1	33	17	7	4	0.01	1	0.6	1.4	26	0.01
KL44-02	36	39	0.0037		37	0.21	0.1	81	11	13	3	0.01	1	0.9	1.3	25	0.16
KL44-02	39	42	0.004		40	0.01	0.1	23	6	4	3	0.01	1	0.3	1.5	21	0.01
KL44-02	42	45	0.0054		54	0.11	0.1	70	30	16	2	0.01	1	1.8	2.3	27	0.18
KL44-02	45	48	0.0031		31	0.04	0.1	59	15	9	5	0.01	1	0.7	1.8	24	0.1
KL44-02	48	51	0.0021		21	0.01	0.1	30	14	2	4	0.01	1	0.8	1.0	25	0.01
KL44-02	51	54	0.0033		33	0.01	0.6	65	29	3	4	0.01	1	0.3	1.3	25	0.01
KL44-02	54	57	0.0054		54	0.06	0.1	27	14	2	3	0.01	1	0.7	1.0	23	0.13
KL44-02	57	60	0.0041		41	0.09	0.1	170	86	15	3	0.01	1	3	2.0	23	0.19
KL44-02	60	63	0.0114		114	0.41	1.9	249	137	70	3	0.01	1	7.3	4.8	37	0.67
KL44-02	63	66	0.0031		31	0.08	0.1	66	65	35	3	0.01	1	2.4	2.8	34	0.11
KL44-02	66	69	0.0042		42	1.07	2.2	272	67	240	4	2	2	6	6.3	41	0.59
KL44-02	69	72	0.0032		32	0.26	0.8	79	45	83	3	0.01	1	2.8	2.8	24	0.19
KL44-02	72	75	0.0046		46	0.07	0.8	124	78	40	2	0.01	1	2.2	3.5	26	0.14
KL44-02	75	78	0.0119		119	0.08	4.7	1210	630	37	11	22	1	1.8	24.6	45	0.01
KL44-02	78	81	0.0105		105	0.1	0.9	198	64	65	34	1	2	2.9	1.8	56	0.11
KL44-02	81	84	0.0166		166	0.13	0.7	267	208	110	9	0.01	4	4.5	2.8	67	0.01
KL44-02	84	87	0.34		3400	1.34	72	41600	3100	510	23	423	20	10.7	135.0	41	1.4
KL44-02	87	88.1	0.0128		128	0.43	7.8	4080	3480	73	7	10	1	6.2	11.3	22	0.77
KL44-02	88.1	91.1	0.101		1010	0.45	15.6	8100	4400	340	28	19	5	90	47.0	48	1.1
KL44-02	91.1	94.1	0.145		1450	3.82	64	14200	6300	960	790	35	4	36	22.5	91	3.09
KL44-02	94.1	97.1	0.052		520	2.24	18.7	6300	1440	560	3000	45	3	14.3	35.0	210	0.74

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL44-02	97.1	100.1	0.026		260	0.67	5.5	2820	870	220	1200	13	2	7.5	13.0	67	0.43
KL44-02	100.1	103.1	0.0147		147	0.26	1	1010	228	170	850	2	3	5.8	5.0	48	0.1
KL44-02	103.1	106.1	0.0101		101	0.28	0.1	650	160	220	1380	2	4	8	7.5	37	0.1
KL44-02	106.1	107.8	0.0093		93	0.11	0.1	140	52	240	1330	7	2	6	11.0	32	0.01
KL44-02	107.8	110.8	0.0026		26	0.02	0.1	387	65	46	268	7	1	3.6	2.8	25	0.01
KL44-02	110.8	113.8	0.118		1180	0.29	1.6	910	115	370	430	4	3	11.1	4.0	33	0.15
KL44-02	113.8	116.8	0.0285		285	0.54	1.8	1010	177	150	450	5	3	9.3	7.0	34	0.28
KL44-02	116.8	119.7	0.0203		203	0.1	1.7	1540	730	61	75	4	1	12	4.5	31	0.12
KL44-02	119.7	122.5	0.0117		117	0.07	1.2	780	264	33	33	2	1	4	3.5	26	0.01
KL44-02	122.5	125.5	0.0358		358	0.06	1.9	2620	540	70	18	10	1	8	7.4	22	0.1
KL44-02	125.5	128.5	0.0154		154	0.08	0.5	570	73	32	33	2	1	3.4	2.8	23	0.01
KL44-02	128.5	131.9	0.0126		126	0.07	0.6	112	39	18	34	2	1	1.3	1.5	24	0.01
KL44-02	131.9	134.5	0.0128		128	0.24	1	1950	257	110	19	1	1	3.7	1.6	20	0.12
KL44-02	134.5	137.5	0.0091		91	0.07	0.7	181	73	13	63	3	2	1.1	2.0	26	0.01
KL44-02	137.5	140.5	0.0196		196	0.06	1.3	500	130	40	70	4	1	14.8	3.0	24	0.01
KL44-02	140.5	143.5	0.0103		103	0.1	0.6	331	80	16	32	3	3	1.6	2.0	24	0.01
KL44-02	143.5	146.5	0.0117		117	0.08	1.6	840	290	44	40	8	1	4.6	4.3	25	0.01
KL44-02	146.5	149.3	0.044		440	0.2	2	2090	145	120	234	11	1	16.6	4.8	33	0.14
KL44-02	149.3	152.3	0.0343		343	0.19	3.8	2600	1490	72	62	11	5	10.6	12.3	33	0.15
KL44-02	152.3	155.5	0.11		1100	0.23	0.6	62	18	1	5	0.01	10	0.01	3.2	30	0.01
KL44-02	155.5	158.3	0.0201		201	0.02	1	970	320	51	39	6	3	3.9	4.5	13	0.01
KL44-02	158.3	161.4	0.0316		316	0.01	1.6	1120	378	82	83	3	3	6.6	10.8	12	0.01
KL44-02	161.4	164.5	0.062		620	0.02	3.1	1720	1090	160	52	5	1	11.1	11.5	12	0.18
KL44-02	164.5	166.8	0.051		510	0.1	1.6	870	232	180	24	1	5	6.5	3.5	11	0.1
KL44-02	166.8	168.4	0.092		920	0.17	1.8	580	116	330	73	2	5	12.1	4.0	13	0.1
KL44-02	168.4	170.5	0.098		980	0.38	4	2960	690	370	34	5	8	15.3	7.4	12	0.28
KL44-02	170.5	173.5	0.137		1370	0.31	4.1	8200	630	420	43	5	7	15	10.0	15	0.38
KL44-02	173.5	174.5	0.097		970	0.22	3.7	2510	980	290	25	4	6	11.8	7.3	13	0.28
KL44-02	174.5	176.5	0.28		2800	0.84	8.8	6400	3300	1010	235	15	14	26	14.5	40	0.62
KL44-02	176.5	179.5	0.67		6700	0.09	14.5	9600	6700	1660	245	32	32	32	16.7	79	1.07
KL44-02	179.5	182.5	0.23		2300	0.62	5.3	5180	2670	490	89	7	36	9.6	13.5	84	0.53
KL44-02	182.5	185.5	0.19		1900	0.5	2.7	6100	2700	250	47	3	18	6.7	10.8	60	0.31
KL44-02	185.5	188.5	0.38		3800	0.43	3.4	4140	2650	350	19	2	13	5.2	7.5	42	0.01
KL44-02	188.5	191.5	0.046		460	0.31	2.5	2410	800	80	21	13	6	2.7	10.0	18	0.01
KL44-02	191.5	193.5	0.04		400	0.13	0.8	1080	257	35	14	1	6	1.7	2.8	17	0.01
KL44-02	193.5	195.7	0.33		3300	1.24	8.5	2320	1070	380	23	2	97	22	4.2	38	0.11
KL44-02	195.7	197.5	0.95		9500	0.55	12.7	29400	3200	140	25	2	94	6.3	29.0	91	0.01
KL44-02	197.5	200.5	1.46		14600	1.38	22.3	21100	118	280	38	0.01	100	4.2	27.0	134	0.39
KL44-02	200.5	203.5	4.5		45000	1.6	26.5	610	109	570	490	1	121	5.8	70.0	121	0.35
KL44-02	203.5	206.5	3.27		32700	1.4	6	355	114	390	250	4	70	4.7	32.5	96	0.5
KL44-02	206.5	207.9	2.23		22300	0.8	2.1	580	78	130	118	8	88	2.6	56.3	113	0.1
KL44-02	207.9	209.7	0.49		4900	0.51	1.4	220	67	61	241	14	24	5.9	21.0	102	0.01
KL44-02	209.7	212.6	0.79		7900	0.28	1.9	96	59	34	1200	8	13	2.2	15.3	43	0.01
KL44-02	212.6	215.5	1.33		13300	0.37	4.3	110	78	50	1350	11	16	2	18.0	40	0.01
KL44-02	215.5	218.5	0.41		4100	0.54	4.9	195	117	65	1350	34	6	1.5	8.8	56	0.01
KL44-02	218.5	221.5	0.64		6400	0.58	3.2	232	131	68	3160	24	8	2.3	11.0	54	0.01
KL44-02	221.5	223.3	1.2		12000	0.8	7.8	225	219	180	2700	95	11	8.3	12.2	56	0.01
KL44-02	223.3	225.2															
KL44-02	225.2	227.5	7.56		75600	3.28	36	2200	580	250	760	7	86	15	27.5	107	0.01
KL44-02	227.5	230.5	1.44		14400	2.72	16.5	3000	560	400	40	0.01	59	26	15.5	62	0.01
KL44-02	230.5	233.5	1.38		13800	2.04	19.7	55500	1580	710	48	1	140	32	44.5	93	0.01
KL44-02	233.5	236.5	1.44		14400	2.44	14.2	17500	2400	340	144	2	60	22	15.5	41	0.01
KL44-02	236.5	239.5	0.94		9400	0.72	7.7	27300	1120	120	22	2	61	4.1	36.0	85	0.1
KL44-02	239.5	241.2	0.156		1560	2.28	17.8	2800	1670	1350	23	2	90	57	4.5	53	0.12
KL44-02	241.2	243.1	0.0224		224	0.31	10.2	6700	2300	220	26	0.01	1	12.3	1.5	19	0.01
KL44-02	243.1	245.5	0.0116		116	0.11	1.5	760	430	62	17	0.01	1	2.6	1.1	16	0.01
KL44-02	245.5	247.8	0.022		220	0.3	2.3	5450	2270	280	31	1	1	12.7	3.0	24	0.01
KL44-02	247.8	249	0.092		920	2.85	25.1	12600	10200	600	35	2	4	33	7.0	30	0.23
KL44-02	249	253	0.0118		118	0.75	1	690	385	200	13	0.01	1	11.5	3.5	14	0.01
KL44-02	253	255.7	0.124		1240	8.69	71	39400	37900	650	27	3	3	81	9.5	39	0.16
KL44-02	255.7	258.1	0.102		1020	2.67	27.6	14700	9250	1000	134	4	6	52	13.2	24	0.39
KL44-02	258.1	259.9	0.24		2400	0.68	6.2	2470	1670	510	57	5	118	26	11.8	35	0.31
KL44-02	259.9	263.1	0.0162		162	0.26	1.2	670	570	120	19	0.01	3	6.3	2.3	20	0.28

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL44-02	263.1	265.8	0.0351		351	0.71	3.4	7800	930	600	18	2	4	14.1	1.6	18	0.47
KL44-02	265.8	267.7	0.0151		151	0.36	1.6	1840	340	230	20	1	1	5.5	1.3	17	0.19
KL44-02	267.7	269.5	0.0142		142	0.47	1.7	940	365	170	18	2	3	11.5	3.3	23	0.31
KL44-02	269.5	272.5	0.18		1800	0.44	1.7	2350	710	120	55	3	11	13.8	4.0	31	0.3
KL44-02	272.5	275.5	0.0058		58	0.18	0.6	950	325	140	16	0.01	2	7.7	1.5	24	0.17
KL44-02	275.5	278.5	0.0219		219	0.09	4.3	1860	2600	67	33	1	5	5.6	1.5	20	0.01
KL44-02	278.5	281.5	0.0206		206	0.24	4.9	3770	1810	120	21	1	3	6.2	3.3	23	0.01
KL44-02	281.5	284.5	0.0065		65	0.1	0.8	820	395	52	4	0.01	2	1.5	0.9	18	0.01
KL44-02	284.5	287.5	0.0096		96	0.7	1	1620	375	310	21	2	4	6.4	3.3	26	0.18
KL44-02	287.5	290.5	0.0225		225	1.18	1.6	3540	1460	430	17	1	4	11.1	3.7	23	0.21
KL44-02	290.5	293.5	0.055		550	0.16	0.6	710	229	99	29	0.01	6	3.3	2.4	23	0.11
KL44-02	293.5	296.5	0.0098		98	0.19	0.5	480	157	86	21	1	4	2.6	1.7	28	0.1
KL44-02	296.5	299.5	0.0257		257	0.26	1.8	1360	1030	73	69	0.01	6	2.7	0.8	35	0.01
KL44-02	299.5	301.7	0.099		990	0.15	2.8	3130	4960	58	98	1	12	3.9	2.5	31	0.01
KL44-02	301.7	304.6	8.59		85900	2.72	55	14400	4100	230	16	3	282	7.6	100.0	35	0.01
KL44-02	304.6	306.7	0.135		1350	2.85	7	6900	5200	480	58	2	7	23	4.7	31	0.32
KL44-02	306.7	308.5	0.027		270	2.77	11.1	17000	12200	450	80	1	4	36	4.0	31	0.24
KL44-02	308.5	311.5	0.093		930	1.36	3	1310	1040	210	56	4	12	14.6	2.3	66	0.01
KL44-02	311.5	314.5	0.53		5300	1.66	5.3	1980	430	440	55	8	51	13.2	11.5	48	0.01
KL44-02	314.5	317.5	0.55		5500	1.76	4.9	294	321	530	131	40	68	5.9	17.5	130	0.01
KL44-02	317.5	320.5	0.084		840	1.68	4.3	3790	2110	170	36	45	100	3.8	9.5	78	0.01
KL44-02	320.5	323.5	0.59		5900	1.92	6.9	820	710	160	74	20	45	2.4	15.3	100	0.01
KL44-02	323.5	326.5	2.64		26400	3	17.6	270	141	100	267	8	64	1.2	33.0	92	0.01
KL44-02	326.5	329.5	0.45		4500	1.82	5.1	260	267	180	102	54	40	2.6	39.5	41	0.01
KL44-02	329.5	331.4	0.307		3070	0.8	7.6	1500	960	180	51	52	61	1.3	53.8	23	0.01
KL44-02	331.4	333	0.312		3120	1.08	4.1	1780	310	330	103	31	56	6.4	12.0	31	0.01
KL44-02	333	335.5	0.045		450	0.73	2.3	3550	560	80	7	14	6	5.4	2.4	30	0.14
KL44-02	335.5	338.5	0.022		220	1.66	3.4	10000	1300	150	18	31	3	14.4	1.5	30	0.14
KL44-02	338.5	341.5	0.016		160	0.22	1.8	5410	2410	44	17	7	3	2.4	1.0	18	0.01
KL44-02	341.5	344.5	0.0198		198	0.24	3.7	6800	6000	53	12	3	3	5.4	3.0	25	0.01
KL44-02	344.5	347.5	0.0398		398	0.05	0.1	231	172	4	10	0.01	4	0.4	0.0	16	0.01
KL44-02	347.5	350.5	0.0182		182	0.02	0.1	460	510	3	13	0.01	2	0.7	0.0	15	0.01
KL44-02	350.5	353.5	0.051		510	0.1	1.4	1820	670	26	18	12	5	1.1	5.8	26	0.01
KL44-02	353.5	356.5	0.0267		267	0.75	1.3	249	375	39	12	5	6	7.4	6.5	49	0.01
KL44-02	356.5	359.5	0.0074		74	0.11	0.1	182	80	9	22	1	4	1.5	1.0	26	0.01
KL44-02	359.5	361.5	0.005		50	0.03	0.1	210	103	4	12	1	3	0.4	0.0	18	0.01
KL44-02	361.5	363.2	0.059		590	0.24	2.3	1150	368	30	16	17	4	0.6	3.0	24	0.01
KL44-02	363.2	365.5	0.364		3640	2.4	5.8	1530	1160	160	41	45	6	6.4	18.7	49	0.01
KL44-02	365.5	368.5	0.43		4300	1.34	4.8	3360	2090	80	85	6	46	6.6	21.5	98	0.01
KL44-02	368.5	371.5	1.59		15900	1.18	19.1	1060	630	39	93	2	75	2.7	38.0	41	0.01
KL44-02	371.5	374.5	0.84		8400	0.8	10.5	720	407	76	284	2	46	4.2	16.5	33	0.01
KL44-02	374.5	377.5	1.49		14900	1.28	8.7	2700	850	150	45	4	109	6.5	26.3	42	0.01
KL44-02	377.5	380.5	0.45		4500	1.2	3.5	1980	2360	260	75	7	39	19.7	17.5	35	0.01
KL44-02	380.5	383.2	1.48		14800	1.68	8.1	2700	470	250	63	6	72	19	22.5	26	0.01
KL44-02	383.2	384.4	1.17		11700	2.82	12.2	8900	1350	160	45	28	68	20	27.0	53	0.1
KL44-02	384.4	386.5	0.52		5200	2.8	13.8	9600	5000	58	98	20	40	14	103.0	54	0.16
KL44-02	386.5	389.5	0.068		680	1.4	4.4	5260	3660	59	40	12	9	19.4	56.8	142	0.12
KL44-02	389.5	392.5	0.0368		368	0.32	1.8	406	980	80	78	5	5	9.8	11.8	39	0.14
KL44-02	392.5	395.5	0.144		1440	0.43	9.4	6900	1830	460	414	29	12	8.7	31.5	42	0.1
KL44-02	395.5	398.5	0.008		80	0.13	0.1	285	149	73	15	1	3	3	1.0	23	0.17
KL44-02	398.5	401.5	0.0132		132	0.3	1.8	368	253	140	22	6	3	8.9	5.0	28	0.01
KL44-02	401.5	404.5	0.064		640	0.61	6.4	6400	1000	430	81	14	36	11.3	12.5	30	0.13
KL44-02	404.5	407.5	0.0224		224	0.37	1.2	1010	630	220	36	3	5	9	5.3	36	0.01
KL44-02	407.5	410.5	0.0214		214	0.16	0.1	141	55	77	25	1	6	3.4	2.3	32	0.01
KL44-02	410.5	413.5	0.0218		218	0.15	4.7	2650	980	120	42	4	6	10.1	6.6	27	0.1
KL44-02	413.5	416.5	0.0153		153	0.5	0.8	2140	1030	180	25	1	6	8.7	4.8	29	0.01
KL44-02	416.5	419.5	0.0116		116	0.07	0.7	291	201	47	12	1	4	1.9	2.0	16	0.01
KL44-02	419.5	422.5	0.0069		69	0.08	0.1	158	76	38	12	1	4	1.7	1.3	16	0.01
KL44-02	422.5	424.6	0.0124		124	0.12	0.1	209	108	55	10	2	6	2.2	2.0	21	0.01
KL44-02	424.6	426.2	0.27		2700	0.42	1.7	90	50	42	27	14	14	1.8	10.4	23	0.01
KL44-02	426.2	428.5	1.26		12600	3.14	4.6	430	55	150	500	39	63	4.8	28.0	51	0.01
KL44-02	428.5	431.5	1.74		17400	1.74	4.2	225	69	69	354	3	40	1.8	23.5	35	0.01
KL44-02	431.5	434.5	0.27		2700	0.32	0.7	221	164	78	215	4	7	2.7	4.8	31	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL44-02	434.5	437.5	0.083		830	0.58	1.1	220	306	220	1500	4	7	11.1	5.0	30	0.01
KL44-02	437.5	439.9	0.4		4000	1.12	1.7	277	186	310	1220	12	10	11.4	11.6	50	0.01
KL44-02	439.9	440.9	0.23		2300	0.14	1	340	183	140	258	1	8	4.8	4.5	42	0.01
KL44-02	440.9	443.5	0.45		4500	0.27	1.9	650	318	910	441	3	7	4.4	7.3	153	0.01
KL44-02	443.5	445.9	0.0035		35	0.03	0.1	25	15	5	6	0.01	1	0.01	0.0	10	0.01
KL44-02	445.9	448	0.151		1510	0.17	0.9	264	139	180	119	3	4	2.1	4.7	125	0.1
KL44-02	448	451	0.22		2200	0.08	0.6	137	87	68	280	2	5	2.3	2.3	56	0.01
KL44-02	451	453.5	0.65		6500	0.26	7	147	1650	35	3620	15	11	3.2	11.0	88	0.1
KL44-02	453.5	455.5	0.57		5700	0.27	8.2	280	840	30	1150	16	9	3.7	10.8	38	0.1
KL44-02	455.5	458.5	0.39		3900	0.16	3.4	164	259	30	1000	30	7	3	5.0	80	0.01
KL44-02	458.5	461.4	0.7		7000	0.39	2	650	161	210	1370	1	8	3.5	8.3	122	0.1
KL44-02	461.4	464.3	1.47		14700	1.37	3.4	216	131	250	52	1	12	4.5	15.0	42	0.1
KL44-02	464.3	467.4	1.4		14000	1.76	2.6	41	14	190	14	2	50	5.5	21.8	30	0.01
KL44-02	467.4	469.2	1.36		13600	1.85	3.6	67	26	280	4	5	123	12.3	33.0	84	0.01
KL44-02	469.2	471.3	1.6		16000	5	6.8	84	36	410	43	41	53	8	23.8	43	0.01
KL44-02	471.3	473.5	0.082		820	0.43	0.6	58	37	120	14	17	4	4.1	4.9	28	0.01
KL44-02	473.5	476.5	0.0053		53	0.04	0.1	25	14	14	3	0.01	1	0.5	0.6	14	0.01
KL44-02	476.5	479.5	0.042		420	0.23	0.1	110	25	100	161	2	1	1.9	3.1	22	0.01
KL44-02	479.5	482.5	0.0115		115	0.04	0.1	12	6	3	3	0.01	3	0.2	0.0	30	0.01
KL44-02	482.5	485.5	0.104		1040	0.29	0.1	101	43	110	70	4	6	2.4	3.9	33	0.01
KL44-02	485.5	488.5	0.098		980	0.38	0.8	1370	600	180	76	4	5	4.5	2.7	28	0.01
KL44-02	488.5	491.5	0.0265		265	0.22	0.1	61	33	130	33	1	3	5.3	2.3	21	0.01
KL44-02	491.5	494.5	0.046		460	0.17	0.1	74	35	110	23	2	3	4.8	4.4	22	0.01
KL44-02	494.5	497.5	0.0218		218	0.06	0.1	25	14	46	6	0.01	2	2.9	2.1	20	0.01
KL44-02	497.5	500.5	0.0081		81	0.02	0.1	13	13	20	4	0.01	1	0.8	1.4	14	0.01
KL44-02	500.5	503.5	0.005		50	0.02	0.1	20	15	15	3	0.01	4	0.8	1.5	14	0.01
KL44-02	503.5	506.5	0.0172		172	0.03	0.1	48	20	41	7	0.01	1	1.8	1.8	24	0.01
KL44-02	506.5	509.5	0.009		90	0.02	0.1	16	14	19	8	0.01	3	0.9	1.1	18	0.01
KL44-02	509.5	512.5	0.0146		146	0.05	0.1	27	13	38	8	2	2	1	1.7	23	0.01
KL44-02	512.5	515.5	0.0032		32	0.02	0.1	9	12	15	3	0.01	3	0.7	1.4	17	0.01
KL44-02	515.5	518.5	0.0036		36	0.02	0.1	13	16	15	5	0.01	1	0.5	1.2	19	0.01
KL44-02	518.5	521.5	0.003		30	0.02	0.1	20	12	33	5	0.01	5	0.6	1.3	20	0.01
KL44-02	521.5	524.5	0.0072		72	0.02	0.1	19	20	47	9	0.01	3	0.8	1.3	25	0.01
KL44-02	524.5	527.5	0.0222		222	0.07	0.1	25	14	68	9	0.01	2	1.6	2.5	25	0.01
KL44-02	527.5	530.5	0.0027		27	0.02	0.1	13	14	24	7	0.01	3	0.5	1.1	23	0.01
KL44-02	530.5	533.5	0.0035		35	0.04	0.1	39	25	34	10	0.01	4	0.6	1.7	24	0.01
KL44-02	533.5	536.5	0.0037		37	0.03	0.1	15	16	26	9	0.01	4	0.6	1.7	19	0.01
KL44-02	536.5	539.5	0.0054		54	0.02	0.1	8	13	6	6	0.01	1	0.3	1.1	13	0.01
KL44-02	539.5	542.5	0.0019		19	0.01	0.1	5	12	8	5	0.01	4	0.01	1.1	18	0.01
KL44-02	542.5	545.5	0.0023		23	0.04	0.1	10	15	22	6	0.01	3	0.5	2.2	32	0.01
KL44-02	545.5	548.5	0.0015		15	0.02	0.1	7	12	4	3	0.01	3	0.2	0.7	18	0.01
KL44-02	548.5	551.5	0.002		20	0.01	0.1	6	10	5	3	0.01	4	0.01	0.5	19	0.01
KL44-02	551.5	554.5	0.0023		23	0.01	0.1	7	13	4	2	0.01	2	0.01	0.5	18	0.01
KL44-02	554.5	557.5	0.0031		31	0.01	0.1	6	15	3	3	0.01	1	0.01	0.6	20	0.01
KL44-02	557.5	560.5	0.0044		44	0.02	0.1	20	24	18	10	0.01	1	0.6	1.2	23	0.01
KL44-02	560.5	563.5	0.0047		47	0.01	0.1	26	16	15	11	0.01	1	0.3	0.6	17	0.01
KL44-02	563.5	566.5	0.0045		45	0.02	0.1	15	12	20	10	0.01	1	0.3	1.9	20	0.01
KL44-02	566.5	569.5	0.0038		38	0.01	0.1	17	10	11	10	0.01	1	0.01	0.7	18	0.01
KL44-02	569.5	572.5	0.0038		38	0.01	0.1	29	12	13	8	0.01	1	0.3	1.2	26	0.01
KL44-02	572.5	575.5	0.0057		57	0.02	0.1	30	24	17	10	0.01	2	0.2	1.1	25	0.01
KL44-02	575.5	578.5	0.0176		176	0.02	0.1	42	15	42	6	0.01	2	0.3	1.4	21	0.01
KL44-02	578.5	581.5	0.0331		331	0.14	0.1	84	33	81	18	1	1	3.5	2.4	20	0.01
KL44-02	581.5	584.5	0.0097		97	0.03	0.1	65	31	26	7	0.01	1	0.5	1.6	24	0.01
KL44-02	584.5	587.5	0.0071		71	0.02	0.1	50	32	21	6	0.01	1	0.3	1.5	25	0.01
KL44-02	587.5	590.5	0.0107		107	0.02	0.1	67	52	27	6	0.01	2	1.2	3.3	28	0.01
KL44-02	590.5	593.5	0.0046		46	0.02	0.1	52	31	36	8	0.01	3	0.6	2.0	24	0.01
KL44-02	593.5	596.5	0.0034		34	0.01	0.1	103	102	22	3	0.01	1	0.5	1.2	21	0.01
KL44-02	596.5	599.5	0.0047		47	0.01	0.1	386	144	19	2	0.01	1	0.6	0.9	22	0.01
KL44-02	599.5	602.5	0.0046		46	0.01	0.1	188	61	15	3	0.01	1	0.4	0.6	23	0.01
KL44-02	602.5	605.5	0.0035		35	0.01	0.1	26	30	21	10	0.01	1	0.2	0.5	16	0.01
KL44-02	605.5	608.5	0.0037		37	0.01	0.1	27	50	40	9	0.01	1	0.4	0.7	26	0.01
KL44-02	608.5	611.5	0.0047		47	0.06	0.1	79	144	64	5	0.01	3	1.3	2.5	40	0.01
KL44-02	611.5	614.5	0.0048		48	0.02	0.7	43	50	21	3	0.01	2	0.7	1.8	21	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL44-02	614.5	617.5	0.0042		42	0.02	0.7	35	25	33	7	0.01	1	1.2	2.1	29	0.01
KL44-02	617.5	620.5	0.003		30	0.02	0.1	33	16	23	6	0.01	2	0.6	2.9	27	0.01
KL44-02	620.5	623.5	0.0023		23	0.04	0.1	50	37	59	7	0.01	1	0.9	3.2	29	0.01
KL44-02	623.5	626.5	0.0017		17	0.05	0.1	37	20	76	23	0.01	1	1.4	3.8	38	0.01
KL44-02	626.5	629.5	0.0024		24	0.03	0.1	34	11	41	8	0.01	2	0.8	4.0	30	0.01
KL44-02	629.5	632.5	0.0013		13	0.06	0.6	56	22	82	19	0.01	3	1.1	6.3	42	0.01
KL44-02	632.5	635.5	0.0021		21	0.04	0.1	78	107	42	9	1	2	0.7	5.5	29	0.01
KL44-02	635.5	638.5	0.0015		15	0.02	0.1	27	10	16	7	0.01	1	0.2	1.6	23	0.01
KL44-02	638.5	640.3	0.0012		12	0.04	0.1	26	12	9	3	0.01	1	0.01	0.7	15	0.01
KL44-02	640.3	643	0.0036		36	0.07	0.1	74	16	11	8	0.01	1	0.2	2.2	20	0.01
KL44-02	643	644.6	0.0019		19	0.08	0.1	36	14	13	6	0.01	1	0.01	2.0	21	0.01
KL44-02	644.6	647.5	0.0021		21	0.08	0.1	252	700	80	6	0.01	2	1.3	6.5	21	0.01
KL44-02	647.5	650.5	0.0018		18	0.13	0.1	162	177	34	14	0.01	2	0.9	7.3	32	0.01
KL44-02	650.5	653.5	0.003		30	0.09	0.1	131	155	30	5	1	1	0.2	1.8	26	0.01
KL44-02	653.5	655.7	0.0032		32	0.17	0.1	113	61	24	9	0.01	1	0.4	3.6	32	0.01
KL44-02	655.7	658.8	0.0029		29	0.19	0.1	78	16	18	5	0.01	1	0.01	1.8	24	0.01
KL44-02	658.8	661.8	0.0046		46	0.09	0.1	94	53	14	3	0.01	1	0.01	0.6	13	0.01
KL44-02	661.8	664.2	0.0095		95	0.18	0.1	165	67	28	18	5	1	0.3	1.8	12	0.01
KL44-02	664.2	665.5	0.0067		67	0.15	0.7	260	85	27	6	3	3	0.6	2.5	15	0.01
KL44-02	665.5	668.5	0.0059		59	0.08	0.1	68	20	15	8	2	2	0.01	0.5	17	0.01
KL44-02	668.5	670.6	0.055		550	0.1	1	830	34	26	6	1	2	0.01	4.1	13	0.01
KL44-02	670.6	672.4	0.0043		43	0.04	0.1	197	47	9	3	1	1	0.01	1.4	14	0.01
KL44-02	672.4	674	0.0187		187	0.08	0.1	56	18	41	116	4	1	0.01	3.1	15	0.01
KL44-02	674	676.4	0.0073		73	0.06	0.1	110	15	15	43	4	1	0.2	0.9	8	0.01
KL44-02	676.4	679.5	0.067		670	0.24	0.1	110	20	43	43	5	1	2	2.2	16	0.01
KL44-02	679.5	682.5	0.0204		204	0.13	0.1	71	48	34	8	4	2	1	1.6	18	0.01
KL44-02	682.5	685.3	0.0097		97	0.08	0.1	246	120	20	20	3	2	0.2	1.8	16	0.01
KL44-02	685.3	688	0.013		130	0.16	10.9	4800	4000	69	43	4	1	16	3.5	19	0.26
KL44-02	688	690.5	0.0191		191	0.12	1.7	700	620	43	75	13	1	0.9	3.1	18	0.01
KL44-02	690.5	693.6	0.0223		223	0.15	0.8	430	259	44	89	7	1	1.1	3.7	20	0.01
KL44-02	693.6	695.5	0.011		110	0.06	0.1	520	129	28	21	2	1	0.5	1.1	14	0.01
KL44-02	695.5	698.5	0.0089		89	0.09	0.9	1410	403	23	13	2	1	2.2	2.5	16	0.1
KL44-02	698.5	701	0.0125		125	0.03	0.1	40	17	5	23	0.01	2	0.01	0.0	12	0.01
KL44-02	701	703.3	0.0065		65	0.07	0.1	45	24	12	4	1	2	0.01	0.7	16	0.01
KL44-02	703.3	705.4	0.0043		43	0.05	0.1	30	16	8	5	1	1	0.2	0.6	15	0.01
KL44-02	705.4	706.7	0.051		510	0.14	0.5	336	157	34	167	3	3	2.6	7.2	114	0.01
KL44-02	706.7	709.2	0.0153		153	0.05	0.1	144	77	12	13	2	2	0.2	1.8	15	0.01
KL44-02	709.2	711.1	0.0042		42	0.01	0.1	47	13	4	9	0.01	2	0.2	0.6	10	0.01
KL44-02	711.1	714.2	0.0034		34	0.02	0.1	163	14	5	10	0.01	1	0.01	0.0	20	0.01
KL44-02	714.2	716.2	0.0041		41	0.04	0.1	39	16	7	10	0.01	1	0.01	0.0	12	0.01
KL44-02	716.2	719.3	0.0084		84	0.03	0.1	40	29	8	7	1	1	0.2	0.0	15	0.01
KL44-02	719.3	722.3	0.0044		44	0.02	0.1	91	25	7	3	0.01	1	0.01	0.0	12	0.01
KL44-02	722.3	723.8	0.0078		78	0.05	0.1	236	100	10	2	0.01	2	0.01	0.6	10	0.01
KL44-02	723.8	727	0.0152		152	0.07	0.1	281	130	14	12	1	1	0.3	1.0	12	0.01
KL44-02	727	729.6	0.0259		259	0.14	0.1	289	214	37	8	0.01	1	1.2	1.7	14	0.01
KL44-02	729.6	731.7	0.059		590	0.15	0.1	112	30	39	12	0.01	1	1.6	1.6	14	0.01
KL44-02	731.7	734.5	0.063		630	0.23	0.8	105	26	38	23	0.01	3	1.1	1.7	17	0.01
KL44-02	734.5	736.5	0.046		460	0.13	0.1	110	16	20	20	0.01	1	0.5	1.3	14	0.01
KL44-02	736.5	739.5	0.0026		26	0.06	0.1	77	17	2	3	0.01	2	0.01	0.0	13	0.01
KL44-02	739.5	740.8	0.0038		38	0.08	0.1	165	16	6	4	0.01	1	0.2	0.0	15	0.01
KL44-02	740.8	743.9	0.0046		46	0.07	0.1	75	13	7	3	0.01	1	0.7	0.0	13	0.01
KL44-02	743.9	746.5	0.22		2200	0.35	2.4	8700	58	90	10	1	38	0.5	14.8	14	0.01
KL44-02	746.5	749.5	0.0071		71	0.04	0.7	242	83	11	3	0.01	1	0.2	0.7	12	0.01
KL44-02	749.5	752.5	0.072		720	0.18	0.8	241	52	70	8	0.01	3	0.01	1.1	10	0.01
KL44-02	752.5	755.5	0.0042		42	0.05	0.1	80	17	9	3	0.01	2	0.4	0.0	10	0.01
KL44-02	755.5	758.5	0.0284		284	0.13	0.8	322	97	18	12	2	1	0.5	2.3	14	0.01
KL44-02	758.5	761.5	0.059		590	0.09	0.6	136	27	7	6	1	3	0.3	1.1	11	0.01
KL44-02	761.5	764.5	0.0109		109	0.05	0.1	152	50	19	3	1	1	0.2	0.8	10	0.01
KL44-02	764.5	766.7	0.0292		292	0.07	0.1	156	43	17	1	0.01	1	1.7	0.9	8	0.01
KL44-02	766.7	769.7	0.192		1920	0.35	1.4	420	177	120	130	2	6	1.2	4.8	19	0.01
KL44-02	769.7	771.3	0.0314		314	0.07	0.6	215	66	29	6	1	3	0.01	1.4	8	0.01
KL44-02	771.3	773.5	0.005		50	0.03	0.1	122	30	6	2	0.01	3	0.01	0.0	11	0.01
KL44-02	773.5	776.6	0.0038		38	0.12	0.1	172	52	6	3	0.01	1	0.6	0.0	14	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL44-02	776.6	779.5	0.0206		206	0.49	1.8	1250	960	24	2	2	3	2.2	2.2	22	0.01
KL44-02	779.5	781.6	0.005		50	0.03	0.1	135	58	6	2	0.01	1	0.01	0.0	14	0.01
KL44-02	781.6	783.8	0.0071		71	0.03	0.1	123	58	10	4	0.01	1	0.01	0.5	13	0.01
KL44-02	783.8	786.7	0.0047		47	0.03	0.1	162	76	10	3	1	1	0.01	0.9	13	0.01
KL44-02	786.7	788.3	0.0042		42	0.04	0.1	208	50	12	3	1	1	0.01	1.2	15	0.01
KL44-02	788.3	790.6	0.0125		125	0.04	0.1	195	70	11	4	1	1	0.01	1.5	12	0.01
KL44-02	790.6	793	0.0045		45	0.04	0.1	470	209	8	4	0.01	1	0.2	2.1	13	0.01
KL44-02	793	794.5	0.0038		38	0.04	0.1	380	104	14	5	0.01	1	0.5	1.0	15	0.01
KL44-02	794.5	797.5	0.0044		44	0.03	0.1	163	83	6	5	0.01	1	0.3	1.0	13	0.01
KL44-02	797.5	800	0.0057		57	0.04	0.1	223	103	11	5	0.01	1	0.01	4.2	19	0.01
KL44-02	800	803.1	0.0068		68	0.05	0.1	237	59	23	7	0.01	1	0.2	2.1	21	0.01
KL44-02	803.1	806.2	0.014		140	0.2	0.1	370	165	33	167	0.01	3	1.3	1.9	42	0.01
KL44-02	806.2	809.3	0.13		1300	0.37	1.1	660	138	62	80	1	5	2.7	2.4	58	0.01
KL44-02	809.3	812.4	0.066		660	0.43	1.2	1250	440	63	283	4	3	5	4.8	46	0.01
KL44-02	812.4	815.5	0.106		1060	0.61	2.1	2600	550	140	98	10	7	8.3	3.7	99	0.01
KL44-02	815.5	818.5	0.17		1700	0.75	3.7	2600	1280	120	131	8	15	8.8	9.5	85	0.01
KL44-02	818.5	821.5	0.251		2510	0.4	1.6	810	155	58	16	2	6	4.1	3.3	51	0.01
KL44-02	821.5	823.9	1.46		14600	1.97	8.5	3900	2300	83	157	2	32	17.5	11.2	127	0.01
KL44-02	823.9	825.5	0.64		6400	1.16	6.5	2840	540	87	44	8	17	2.7	10.2	23	0.01
KL44-02	825.5	827.5	0.457		4570	0.77	6.7	3510	850	98	43	28	8	2.3	12.0	22	0.01
KL44-02	827.5	830.5	0.72		7200	1.23	20.3	28000	7800	200	76	78	12	10.3	24.5	25	0.15
KL44-02	830.5	832.9	0.29		2900	0.86	8.5	10200	3700	180	51	42	3	5	15.0	24	0.1
KL44-02	832.9	835.3	0.021		210	0.11	0.8	2150	1210	36	9	4	1	1.3	3.3	18	0.01
KL44-02	835.3	836.5	0.0337		337	0.32	3.5	4040	3660	84	18	14	1	2.2	12.9	22	0.1
KL44-02	836.5	838.8	0.0041		41	0.07	0.1	670	335	13	2	2	1	0.3	2.4	14	0.01
KL44-03	47.8	50.2															
KL44-03	50.2	52.9															
KL44-03	52.9	55.9															
KL44-03	55.9	59															
KL44-03	59	62.1															
KL44-03	62.1	65.2															
KL44-03	65.2	68.3															
KL44-03	68.3	71.4															
KL44-03	71.4	74.5															
KL44-03	74.5	77.5															
KL44-03	77.5	80.7															
KL44-03	80.7	83.8															
KL44-03	83.8	86.8															
KL44-03	86.8	89.6															
KL44-03	89.6	91															
KL44-03	91	92															
KL44-03	92	94.7															
KL44-03	94.7	97.4															
KL44-03	97.4	100.2															
KL44-03	100.2	103.1															
KL44-03	103.1	105.5															
KL44-03	105.5	107.8															
KL44-03	107.8	110															
KL44-03	110	112.2															
KL44-03	112.2	113.8															
KL44-03	113.8	116.8															
KL44-03	116.8	118.7															
KL44-03	118.7	120.4															
KL44-03	120.4	122.8															
KL44-03	122.8	125															
KL44-03	125	128.8															
KL44-03	128.8	130.6															
KL44-03	130.6	133.4															
KL44-03	161	163.2															
KL44-03	163.2	164.8	0.0121		121	0.2	1.7	386	450	81	120	6	1	4.2	5.5	26	0.01
KL44-03	164.8	167.8	0.017		170	0.12	3	570	780	77	114	14	1	8.8	10.0	30	0.01
KL44-03	167.8	170.8	0.062		620	0.18	9.5	4530	6300	180	158	22	1	30	27.7	33	0.01
KL44-03	170.8	173.5	0.007		70	0.06	1.5	1380	1030	24	21	5	1	1.8	8.8	14	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL44-03	173.5	176.4	0.0048		48	0.05	1.3	640	730	16	16	4	1	1.6	5.3	15	0.01
KL44-03	176.4	179.1	0.0381		381	0.09	3.2	2570	2480	73	100	8	1	10.3	14.6	11	0.01
KL44-03	179.1	182.8	0.015		150	0.05	1.5	640	500	39	9	5	1	6	4.0	13	0.01
KL44-03	182.8	185.5	0.0345		345	0.06	1.2	900	224	130	11	6	1	7.2	4.3	16	0.01
KL44-03	185.5	188.8	0.117		1170	0.1	20.4	1610	3300	350	38	60	1	25	40.0	15	0.01
KL44-03	188.8	191.4	0.044		440	0.04	2.6	800	620	150	23	6	1	5.1	4.0	13	0.01
KL44-03	191.4	194.7	0.0114		114	0.07	1.7	990	890	50	14	6	1	3.8	5.0	15	0.01
KL44-03	194.7	197.6	0.0187		187	0.1	2.2	1400	1160	52	22	9	1	3.7	8.8	14	0.01
KL44-03	197.6	200.8	0.057		570	0.2	3.9	4700	3900	59	29	14	1	2.4	13.8	18	0.01
KL44-03	200.8	203.8	0.0161		161	0.35	2.3	800	550	72	26	9	1	2.2	5.0	18	0.1
KL44-03	203.8	207.2	0.093		930	0.45	12	5900	1830	240	72	68	1	25	18.5	21	0.22
KL44-03	207.2	209.8	0.101		1010	0.25	5	2240	850	330	108	32	1	15.2	9.3	16	0.1
KL44-03	209.8	212.8	0.065		650	0.13	1.8	1340	210	180	67	18	1	5.9	7.0	16	0.12
KL44-03	212.8	215.3	0.081		810	0.22	2.5	2600	261	240	54	24	1	8	10.5	15	0.22
KL44-03	215.3	217	0.0338		338	0.11	1.6	3800	90	48	32	44	1	0.9	9.6	13	0.01
KL44-03	217	220	0.04		400	0.1	1.2	930	109	50	16	16	1	1.1	5.5	14	0.01
KL44-03	220	221.9	0.057		570	0.1	1.1	1600	115	150	13	7	1	1.2	5.3	13	0.01
KL44-03	221.9	224.8	0.0268		268	0.06	1.6	1670	530	61	17	26	1	1.2	6.0	15	0.01
KL44-03	224.8	226.7	0.56		5600	0.53	10.8	5500	480	530	57	84	11	2.8	60.8	31	0.23
KL44-03	226.7	228.6	0.83		8300	0.97	9.4	3780	400	1040	60	38	46	7.7	41.5	60	0.48
KL44-03	228.6	230.8	0.102		1020	0.15	1.6	1080	108	260	33	9	2	2.5	7.3	19	0.01
KL44-03	230.8	233.8	0.074		740	0.15	1.5	2990	312	150	17	26	3	2.6	7.5	18	0.12
KL44-03	233.8	235.7	0.162		1620	0.26	2.2	6700	440	440	14	40	3	5.6	15.0	23	0.2
KL44-03	235.7	238.8	0.65		6500	0.5	3.6	5200	180	680	13	9	5	9.3	15.0	25	0.12
KL44-03	238.8	241.8	0.33		3300	0.45	5.1	9200	346	170	24	28	6	3.1	27.3	26	0.15
KL44-03	241.8	243.6	0.121		1210	0.19	0.8	1200	84	170	43	6	4	5.2	6.0	16	0.1
KL44-03	243.6	244.8	0.198		1980	0.27	1.2	336	49	650	7	28	3	12.8	13.0	18	0.24
KL44-03	244.8	247.9	0.23		2300	0.47	1.7	1140	60	770	16	22	5	25	19.4	37	0.38
KL44-03	247.9	251	0.94		9400	1.34	4.2	500	77	3500	46	22	31	55	53.5	56	1.05
KL44-03	251	253.1	0.51		5100	1	2.3	400	126	2030	36	9	14	35	13.5	33	0.57
KL44-03	253.1	254.8	0.141		1410	0.17	0.9	490	43	450	11	3	4	4.1	4.5	17	0.1
KL44-03	254.8	257.8	0.58		5800	0.72	1.4	710	76	520	9	8	25	4.6	33.5	75	0.2
KL44-03	257.8	260.8	0.52		5200	0.88	2.2	570	32	200	22	7	22	11.2	18.3	52	0.42
KL44-03	260.8	263.8	0.58		5800	0.96	3.3	3200	123	1070	15	3	12	5.8	18.0	53	0.34
KL44-03	263.8	266.8	0.26		2600	0.33	1.7	960	48	77	27	1	16	3.4	2.3	53	0.01
KL44-03	266.8	269.8	0.55		5500	0.67	1.3	178	48	100	28	1	21	4.7	13.5	35	0.01
KL44-03	269.8	272.8	0.4		4000	0.29	3.6	5500	6400	130	359	3	18	3.8	13.3	33	0.38
KL44-03	272.8	275.8	0.39		3900	0.33	6.8	11800	8600	260	580	3	25	3.7	14.6	137	0.58
KL44-03	275.8	278.8	0.23		2300	0.37	2.3	790	650	500	31	0.01	17	7.5	8.5	78	0.1
KL44-03	278.8	281.5	0.24		2400	0.31	1.9	1150	309	310	269	0.01	20	6.8	5.0	55	0.18
KL44-03	281.5	283.3	0.64		6400	0.32	2	4350	250	350	156	0.01	29	3.4	10.8	120	0.16
KL44-03	283.3	284.8	0.21		2100	0.39	1.1	500	100	78	810	0.01	17	2.3	6.9	100	0.01
KL44-03	284.8	287.8	0.64		6400	0.67	1.8	370	102	57	132	0.01	16	2.1	11.5	31	0.01
KL44-03	287.8	290.8	0.505		5050	0.52	2.4	120	22	45	22	0.01	10	1.6	8.3	47	0.01
KL44-03	290.8	293.8	1.03		10300	0.55	2.3	118	14	40	80	0.01	19	2.4	13.0	54	0.01
KL44-03	293.8	296.8	0.61		6100	0.46	1.8	67	13	32	153	0.01	16	1.1	22.0	26	0.01
KL44-03	296.8	299.8	0.26		2600	0.26	0.9	1220	167	240	16	0.01	20	2.3	10.8	26	0.01
KL44-03	299.8	302.8	0.387		3870	0.31	0.6	68	20	10	40	0.01	18	0.3	6.3	34	0.01
KL44-03	302.8	305.8	0.99		9900	0.65	2.2	79	10	17	87	0.01	21	0.8	9.5	27	0.01
KL44-03	305.8	308.8	0.61		6100	0.54	1.4	293	52	53	27	0.01	15	1.2	10.5	44	0.22
KL44-03	308.8	311.8	0.407		4070	0.29	0.9	83	14	23	173	0.01	14	0.7	6.8	39	0.1
KL44-03	311.8	314.8	0.344		3440	0.4	1.3	560	30	86	145	0.01	30	1.2	10.3	55	0.01
KL44-03	314.8	317.8	1.07		10700	0.43	3.8	1790	148	250	154	1	35	3.4	12.2	31	0.16
KL44-03	317.8	320.8	0.62		6200	0.32	1.2	780	122	95	39	0.01	18	6	9.0	46	0.01
KL44-03	320.8	323.8	0.76		7600	0.44	1.2	141	41	79	24	0.01	14	3.3	7.3	47	0.01
KL44-03	323.8	326.8	0.8		8000	0.52	1.7	191	73	51	36	0.01	17	2	9.3	65	0.01
KL44-03	326.8	329.8	0.425		4250	0.41	1.9	2520	3600	180	67	1	19	5.4	13.2	78	0.38
KL44-03	329.8	332.8	0.346		3460	0.21	1	311	112	230	120	0.01	11	6.6	3.0	30	0.1
KL44-03	332.8	335.8	0.438		4380	0.27	1.5	81	45	8	79	0.01	9	0.8	4.9	20	0.01
KL44-03	335.8	337	0.364		3640	0.21	1.1	81	24	8	27	0.01	10	0.5	4.0	14	0.01
KL44-03	337	338.8	0.57		5700	0.37	1.2	133	40	37	7	0.01	20	2.6	7.0	33	0.01
KL44-03	338.8	341.8	0.54		5400	0.45	1.3	141	52	60	235	1	19	4.8	6.3	36	0.01
KL44-03	341.8	344.8	0.78		7800	0.43	1.4	870	213	110	138	2	32	5.7	8.8	30	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL44-03	524.8	526.6														
KL44-03	526.6	528.5														
KL44-03	528.5	528.8														
KL44-03	528.8	533.8														
KL44-03	533.8	536.8														
KL44-03	536.8	539.8														
KL44-03	539.8	542.8														
KL44-03	542.8	545.8														
KL44-03	545.8	548.8														
KL44-03	548.8	551.8														
KL44-03	551.8	554.8														
KL44-03	554.8	557.8														
KL44-03	557.8	560.8														
KL44-03	560.8	563.8														
KL44-03	563.8	566.8														
KL44-03	566.8	570.9														
KL44-03	570.9	572.8														
KL44-03	572.8	575.8														
KL44-03	575.8	578.8														
KL44-03	578.8	581.8														
KL44-03	581.8	584.8														
KL44-03	584.8	587.8														
KL44-03	587.8	591.8														
KL44-03	591.8	594.8														
KL44-03	594.8	596.8														
KL44-03	596.8	599.8														
KL44-03	599.8	602.8														
KL44-03	602.8	605.8														
KL44-03	605.8	608.8														
KL44-03	608.8	611.8														
KL44-03	611.8	614.8														
KL44-03	614.8	617.9														
KL44-03	617.9	620.8														
KL44-03	620.8	623.8														
KL44-03	623.8	626.8														
KL44-03	626.8	629.8														
KL44-03	629.8	632.8														
KL44-03	632.8	635.8														
KL44-03	635.8	638.8														
KL44-03	638.8	641.6														
KL44-03	641.6	644.8														
KL44-03	644.8	647.8														
KL44-03	647.8	650.8														
KL44-03	650.8	653.8														
KL44-03	653.8	656.8														
KL44-03	656.8	659.8														
KL44-03	659.8	662.8														
KL44-03	662.8	665.8														
KL44-03	665.8	668.8														
KL44-03	668.8	671.8														
KL44-03	671.8	674.8														
KL44-03	674.8	677.8														
KL44-03	677.8	680														
KL44-03	680	682.8														
KL44-03	682.8	686.8														
KL44-03	686.8	689.8														
KL44-03	689.8	692.8														
KL44-03	692.8	695.8	1.72	17200	1.26	3.3	88	12	2	98	1	18	0.01	17.5	26	0.01
KL44-03	695.8	698.8	1.73	17300	1.04	3.4	72	7	4	219	1	19	0.01	12.5	11	0.01
KL44-03	698.8	701.8	1.27	12700	0.94	2.4	80	22	14	31	1	13	0.5	17.0	30	0.01
KL44-03	701.8	704.8	1.02	10200	0.84	2.3	69	16	31	23	2	10	0.6	12.5	29	0.01
KL44-03	704.8	707.6	0.9	9000	0.83	1.8	54	19	34	32	1	10	0.8	15.8	26	0.01
KL44-03	707.6	710.7	0.63	6300	0.43	1.5	100	24	34	15	3	11	4.8	17.8	28	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL44-03	892.7	895.8															
KL44-03	895.8	898.9															
KL44-03	898.9	902															
KL44-03	902	905.1															
KL44-03	905.1	908.2															
KL44-03	908.2	909.9															
KL44-03	909.9	912.3															
KL44-03	912.3	914.4															
KL44-03	914.4	917.5															
KL44-03	917.5	920.6															
KL44-03	920.6	923.7															
KL44-03	923.7	924.1															
KL44-03	924.1	926.8															
KL44-03	926.8	929.8															
KL44-03	929.8	932.8															
KL44-03	932.8	935.8															
KL44-03	935.8	938.1															
KL44-03	938.1	941.2															
KL44-03	941.2	944.3															
KL44-03	944.3	947.4															
KL44-03	947.4	950.4															
KL44-04	0	2.5	0.0088		88	0.01	0.7	121	78	12	4	0.01	1	0.6	1.3	16	0.01
KL44-04	2.5	5.1	0.005		50	0.01	0.8	90	56	8	3	0.01	1	0.5	1.2	17	0.01
KL44-04	5.1	8.1	0.0064		64	0.01	0.7	137	107	8	2	0.01	1	0.5	1.6	23	0.01
KL44-04	8.1	11.2	0.0047		47	0.01	0.6	55	50	10	3	0.01	1	0.2	1.7	25	0.01
KL44-04	11.2	14.3	0.0073		73	0.01	0.8	109	85	9	3	0.01	1	0.5	2.1	31	0.01
KL44-04	14.3	17.4	0.0028		28	0.01	0.9	54	34	7	3	0.01	1	0.5	1.5	22	0.01
KL44-04	17.4	20.5	0.0023		23	0.01	0.1	99	28	12	3	0.01	1	1	1.8	23	0.01
KL44-04	20.5	23.6	0.0022		22	0.01	0.1	16	17	9	3	0.01	1	0.5	0.7	18	0.01
KL44-04	23.6	26.6	0.0027		27	0.01	0.1	48	61	8	3	0.01	1	0.01	2.1	23	0.01
KL44-04	26.6	29.6	0.002		20	0.01	0.1	101	36	3	1	0.01	1	0.01	0.0	19	0.01
KL44-04	29.6	32.5	0.0073		73	0.01	0.1	30	24	5	1	0.01	1	0.01	0.5	23	0.01
KL44-04	32.5	35.6	0.0039		39	0.01	0.1	36	28	2	1	0.01	1	0.01	0.0	17	0.01
KL44-04	35.6	38.6	0.004		40	0.18	0.1	47	45	23	2	0.01	1	1.6	1.1	22	0.01
KL44-04	38.6	41.6	0.0034		34	1.22	2.5	132	75	35	1	0.01	1	3.7	2.9	30	0.38
KL44-04	41.6	44.5	0.0023		23	0.15	0.7	150	76	22	1	0.01	1	1.7	2.3	28	0.15
KL44-04	44.5	47.5	0.0033		33	0.14	1	75	49	45	3	0.01	1	2.5	3.2	47	0.25
KL44-04	47.5	50.6	0.0063		63	0.07	2.4	700	247	44	2	0.01	1	2.3	4.3	32	0.2
KL44-04	50.6	53.6	0.007		70	0.03	0.1	128	38	29	3	0.01	1	0.8	1.1	38	0.01
KL44-04	53.6	56.6	0.008		80	0.01	0.1	70	31	13	19	0.01	1	1.1	1.1	17	0.01
KL44-04	56.6	59.6	0.0022		22	0.01	0.1	24	18	12	2	0.01	1	0.01	1.0	15	0.01
KL44-04	59.6	62.6	0.0032		32	0.01	0.1	31	27	14	2	0.01	1	0.5	1.7	20	0.01
KL44-04	62.6	65.6	0.004		40	0.01	0.1	50	32	13	2	0.01	1	0.7	1.6	20	0.01
KL44-04	65.6	68.6	0.0023		23	0.01	0.1	44	27	15	1	0.01	1	0.5	1.7	21	0.01
KL44-04	68.6	71.6	0.0027		27	0.01	0.1	190	127	16	3	0.01	1	1.6	3.3	17	0.01
KL44-04	71.6	74.6	0.0018		18	0.01	0.7	35	39	17	3	0.01	1	1.1	2.4	21	0.01
KL44-04	74.6	77.6	0.0021		21	0.01	0.8	55	69	16	2	0.01	1	1	1.5	20	0.01
KL44-04	77.6	80.6	0.003		30	0.01	1.8	157	150	16	2	0.01	1	1.3	2.6	25	0.01
KL44-04	80.6	83.3	0.004		40	0.01	3.3	89	150	19	4	0.01	1	1.2	1.8	23	0.01
KL44-04	83.3	86.4	0.0092		92	0.01	16	5600	5100	53	6	0.01	1	14.4	57.6	22	0.01
KL44-04	86.4	89.5	0.0036		36	0.01	2.1	264	430	16	5	0.01	1	2.4	2.6	27	0.01
KL44-04	89.5	92.6	0.066		660	0.05	110	41500	37800	180	12	5	4	80	395.0	25	0.17
KL44-04	92.6	95.6	0.0039		39	0.03	9.1	4100	1420	42	4	0.01	1	3.3	31.5	16	0.29
KL44-04	95.6	98.6	0.0037		37	0.08	6.2	1550	1150	73	7	0.01	1	5.1	18.2	22	0.53
KL44-04	98.6	101.6	0.0038		38	0.02	2	420	413	77	6	0.01	1	3.1	2.8	21	0.31
KL44-04	101.6	104.6	0.0022		22	0.02	2.4	284	316	33	5	0.01	1	1.9	4.1	25	0.15
KL44-04	104.6	107.6	0.0033		33	0.01	1.4	110	118	22	3	0.01	1	1	1.1	25	0.1
KL44-04	107.6	110.6	0.002		20	0.01	1.8	169	151	21	7	0.01	2	4.4	3.4	31	0.52
KL44-04	110.6	113.6	0.006		60	0.02	1.1	560	164	17	6	0.01	1	4	2.1	25	0.46
KL44-04	113.6	116.6	0.0028		28	0.01	1.1	159	153	26	4	0.01	1	3.9	2.8	30	0.26
KL44-04	116.6	119.6	0.0017		17	0.01	0.8	70	73	14	4	0.01	1	1.1	1.0	24	0.01
KL44-04	119.6	122.6	0.0034		34	0.01	0.6	55	83	17	4	0.01	1	1	1.7	26	0.01
KL44-04	122.6	125.6	0.0038		38	0.02	1	164	147	34	3	0.01	1	2.3	1.7	29	0.12

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL44-04	125.6	128.6	0.0026		26	0.06	2.8	376	600	36	2	0.01	2	5.6	3.6	22	0.67
KL44-04	128.6	131.6	0.0018		18	0.01	0.8	88	183	34	3	0.01	2	1.6	8.7	21	0.16
KL44-04	131.6	134.6	0.0031		31	0.03	0.1	101	124	19	3	0.01	1	2	1.9	17	0.01
KL44-04	134.6	137.6	0.0033		33	0.07	0.1	116	93	59	2	0.01	2	3.3	2.6	16	0.16
KL44-04	137.6	140.6	0.0022		22	0.05	0.1	312	381	41	2	0.01	1	2.1	1.8	17	0.01
KL44-04	140.6	143.6	0.0026		26	0.03	0.1	415	600	42	2	0.01	1	3.4	1.9	20	0.01
KL44-04	143.6	146.6	0.0032		32	0.02	0.6	120	111	36	2	0.01	1	3.7	3.5	24	0.1
KL44-04	146.6	149.6	0.0022		22	0.02	0.1	106	176	27	3	0.01	1	1.3	3.1	29	0.1
KL44-04	149.6	152.6	0.0073		73	0.02	0.8	274	143	31	7	0.01	3	14.2	1.5	21	0.14
KL44-04	152.6	155.6	0.0288		288	0.09	3.5	1140	420	120	6	1	1	70	9.5	27	0.72
KL44-04	155.6	158.6	0.0076		76	0.13	1.1	930	311	100	17	5	2	34	5.2	28	0.17
KL44-04	158.6	161.6	0.0127		127	0.19	2.3	1030	412	130	6	5	1	17.1	7.5	22	0.37
KL44-04	161.6	164.6	0.0066		66	0.22	1.9	580	271	100	4	2	2	10.6	4.2	31	0.26
KL44-04	164.6	167.6	0.0062		62	0.1	2	3200	1190	120	3	0.01	1	7.8	2.0	28	0.31
KL44-04	167.6	170.6	0.006		60	0.03	0.7	930	269	83	2	0.01	2	8	3.2	30	0.16
KL44-04	170.6	173.6	0.0224		224	0.02	1	890	352	54	2	2	1	4.4	2.5	30	0.32
KL44-04	173.6	176.6	0.0025		25	0.21	0.6	2050	359	140	16	2	2	17.3	5.4	65	2.09
KL44-04	176.6	179.6	0.0132		132	0.11	0.1	239	61	120	4	0.01	3	10.2	1.8	73	0.13
KL44-04	179.6	182.6	0.0105		105	0.77	0.1	420	197	140	17	0.01	2	12.3	5.8	100	0.94
KL44-04	182.6	185.6	0.009		90	1.31	0.1	342	153	91	17	1	6	13.3	5.8	94	0.84
KL44-04	185.6	188.2	0.63		6300	1.18	41	11000	10300	610	75	88	50	9.9	30.0	72	0.56
KL44-04	188.2	189.8	0.835		8350	1.16	295	109000	96000	2600	18	344	14	540	164.0	92	19.8
KL44-04	189.8	191.6	1.06		10600	1.32	107	28500	26600	1920	135	52	4	590	27.0	125	8.4
KL44-04	191.6	193.1	4.77		47700	3.13	257	11800	4100	16000	93	150	3	2780	32.5	180	21
KL44-04	193.1	194.6	0.34		3400	0.25	95	8000	12400	1240	16	10	2	820	8.6	186	4.39
KL44-04	194.6	196.5	0.136		1360	0.27	40	8300	9300	490	26	8	1	222	7.3	127	2.3
KL44-04	196.5	198.7	0.0377		377	0.81	34	18300	16300	230	14	2	3	136	18.5	157	3.86
KL44-04	198.7	200.6	0.06		600	1.34	37	24300	14700	290	140	2	3	178	15.0	130	4.41
KL44-04	200.6	203.6	0.0341		341	1.83	39	18500	11400	330	35	0.01	4	86	12.8	125	5.7
KL44-04	203.6	206.6	0.0186		186	1.73	16.5	7700	5700	300	247	0.01	1	60	6.6	96	0.81
KL44-04	206.6	208.6	0.0071		71	0.62	6.7	4200	1670	140	5	0.01	1	20	2.8	160	0.44
KL44-04	208.6	210.2	0.0064		64	0.79	7.8	3520	3200	160	10	0.01	1	22	5.1	103	0.41
KL44-04	210.2	211.8	0.0045		45	0.44	3.4	1790	1380	90	13	0.01	1	10.8	3.8	106	0.2
KL44-04	211.8	214.9	0.0047		47	0.08	0.7	770	403	22	10	0.01	1	4.4	1.0	143	0.11
KL44-04	214.9	216.4	0.0406		406	0.12	2	1190	1690	82	3	2	1	58	4.2	40	0.16
KL44-04	216.4	218.5	0.0156		156	0.06	0.9	720	366	35	3	1	3	15.4	1.4	24	0.12
KL44-04	218.5	221.4	0.003		30	0.22	3.1	1560	1260	61	187	0.01	1	8.8	2.2	122	0.27
KL44-04	221.4	224.6	0.0035		35	0.53	3.9	5900	2690	160	126	4	1	17	9.2	65	0.91
KL44-04	224.6	226.5	0.0022		22	0.1	0.8	1570	480	75	77	0.01	1	8	3.5	92	0.12
KL44-04	226.5	229.6	0.0143		143	0.2	0.6	1360	276	43	26	0.01	1	5.8	3.6	38	0.1
KL44-04	229.6	231.1	0.0095		95	0.12	0.8	750	178	37	5	0.01	1	3.7	1.3	24	0.01
KL44-04	231.1	233.6	0.0025		25	0.53	2.2	4130	1220	110	29	0.01	3	15.8	5.8	90	0.24
KL44-04	233.6	236.6	0.0126		126	0.56	1.2	3000	820	130	17	0.01	4	24	3.1	64	0.21
KL44-04	236.6	239.5	0.0021		21	0.17	0.6	1190	252	61	18	0.01	1	7.1	2.0	74	0.11
KL44-04	239.5	242.6	0.003		30	1.02	1.4	3420	1100	190	62	0.01	1	28	7.3	93	0.52
KL44-04	242.6	245.6	0.0017		17	0.88	1.1	2940	510	180	35	0.01	1	32	5.1	149	0.54
KL44-04	245.6	248.6	0.0038		38	0.74	1.9	1580	470	250	1020	1	2	34	7.4	51	0.75
KL44-04	248.6	249.8	0.0057		57	0.76	1.7	2860	440	260	620	1	2	36	5.9	48	0.88
KL44-04	249.8	253.9	0.0029		29	0.5	1.1	1840	283	110	201	0.01	1	19.8	2.6	59	0.52
KL44-04	253.9	256.5	0.006		60	1.78	2.2	5250	1610	370	179	1	3	62	4.1	84	3.68
KL44-04	256.5	259	0.008		80	2	11.8	3810	3640	390	1800	38	9	50	32.0	60	2.22
KL44-04	259	262.2	0.19		1900	0.56	3.3	1750	880	710	54	6	40	37	41.0	64	0.35
KL44-04	262.2	264.5	0.0032		32	0.12	0.1	940	277	54	24	2	1	4.4	2.5	30	0.01
KL44-04	264.5	267.4	0.0125		125	0.17	2.1	1480	1040	89	46	4	1	20	14.8	34	0.21
KL44-04	267.4	270.4	0.0061		61	0.12	2.3	1830	1400	58	15	7	1	6.2	17.7	19	0.15
KL44-04	270.4	272.9	0.0242		242	0.15	1.1	298	196	100	139	4	1	15.4	4.3	18	0.1
KL44-04	272.9	275.5	0.0197		197	0.13	2.1	1210	480	140	106	37	1	28	6.5	20	0.12
KL44-04	275.5	278.7	0.0059		59	0.12	0.8	480	171	33	51	14	1	6.9	3.0	18	0.01
KL44-04	278.7	281.6	0.0047		47	0.02	0.1	302	148	27	28	3	1	9.3	4.8	18	0.01
KL44-04	281.6	284.6	0.0142		142	0.06	0.7	1080	411	75	21	3	1	15.3	7.1	26	0.13
KL44-04	284.6	287.5	0.0042		42	0.09	0.6	1010	208	63	10	7	1	6.2	3.2	22	0.01
KL44-04	287.5	289.5	0.0058		58	0.02	2	910	1670	18	14	12	1	2.8	19.3	17	0.01
KL44-04	289.5	291.7	0.0016		16	0.02	0.5	178	152	16	11	11	1	1.4	2.6	21	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL44-04	291.7	294	0.0028		28	0.12	0.7	540	168	25	34	16	1	3.9	8.4	22	0.01
KL44-04	294	296.7	0.0074		74	0.04	5	420	570	36	10	46	1	4.9	6.7	23	0.01
KL44-04	296.7	299	0.003		30	0.05	4.8	282	690	28	9	36	1	4.1	8.2	20	0.01
KL44-04	299	300.9	0.0045		45	0.07	2.4	1180	840	36	13	16	1	5.2	7.6	23	0.1
KL44-04	300.9	303.4	0.0043		43	0.02	0.5	234	141	17	9	7	1	2.7	4.8	23	0.01
KL44-04	303.4	308.2	0.0043		43	0.05	2.4	490	520	2	14	14	1	2.9	7.9	19	0.1
KL44-04	308.2	309.7	0.0049		49	0.07	0.8	243	238	17	10	16	1	6.3	5.2	20	0.01
KL44-04	309.7	312.7	0.0021		21	0.04	0.6	147	168	21	6	12	1	3.3	4.1	22	0.01
KL44-04	312.7	315.3	0.0016		16	0.04	0.6	297	340	32	5	10	1	2	7.8	22	0.01
KL44-04	315.3	316.9	0.003		30	0.03	0.6	309	219	23	9	5	1	3	5.3	23	0.01
KL44-04	316.9	319.1	0.0018		18	0.02	0.8	950	450	11	7	6	1	1.1	5.2	32	0.01
KL44-04	319.1	321.5	0.0021		21	0.06	0.6	235	182	9	7	5	1	3.3	3.6	28	0.01
KL44-04	321.5	324.4	0.0043		43	0.34	1.3	1630	790	67	9	6	1	16.2	6.3	48	0.44
KL44-04	324.4	327.4	0.0324		324	0.04	2.9	1490	490	110	15	10	1	22	4.8	30	0.31
KL44-04	327.4	329.4	0.0019		19	0.01	0.1	230	101	3	13	4	1	1.6	1.6	23	0.01
KL44-04	329.4	332.1	0.003		30	0.02	0.7	187	134	7	7	7	1	3.3	2.6	23	0.01
KL44-04	332.1	335	0.0026		26	0.02	0.8	283	132	7	4	5	1	4.8	2.0	19	0.01
KL44-04	335	337.7	0.0038		38	0.01	0.5	123	89	5	4	8	1	8	3.5	26	0.01
KL44-04	337.7	341	0.0037		37	0.01	0.9	560	237	8	5	4	1	5.4	2.7	15	0.01
KL44-04	341	343.5	0.0038		38	0.01	1.1	402	175	8	21	9	1	6.2	2.1	10	0.01
KL44-04	343.5	346.3	0.0119		119	0.06	2.3	430	267	37	13	19	1	28	3.4	11	0.1
KL44-04	346.3	348.3	0.0018		18	0.01	2.1	319	276	4	11	12	1	3.1	3.3	11	0.01
KL44-04	348.3	350.2	0.0014		14	0.01	0.1	175	98	6	6	1	1	1.2	1.5	10	0.01
KL44-04	350.2	352.7	0.004		40	0.01	0.1	221	253	2	8	1	1	0.5	1.0	10	0.01
KL44-04	352.7	354.7	0.0014		14	0.01	0.1	281	262	1	7	1	1	0.3	1.7	8	0.01
KL44-04	354.7	356.8	0.0022		22	0.01	0.1	213	197	3	4	2	1	1.9	1.6	15	0.01
KL44-04	356.8	358.9	0.0041		41	0.01	0.1	710	340	2	4	1	1	0.5	1.5	14	0.01
KL44-04	358.9	361.2	0.0009		9	0.01	0.1	410	292	2	4	0.01	2	2.3	2.4	13	0.01
KL44-04	361.2	364.5	0.0007		7	0.01	0.1	420	336	1	3	0.01	1	1.2	2.0	15	0.01
KL44-04	364.5	367.3	0.001		10	0.01	0.1	165	89	1	3	0.01	1	0.7	1.4	10	0.01
KL44-04	367.3	370.7	0.0055		55	0.01	0.1	344	120	3	5	4	1	3.3	3.6	15	0.01
KL44-04	370.7	373.2	0.0031		31	0.01	0.1	152	47	0.01	10	1	1	1	1.2	10	0.01
KL44-04	373.2	375.8	0.0017		17	0.01	0.1	145	79	2	7	1	1	2.4	0.9	11	0.01
KL44-04	375.8	377.8	0.0009		9	0.01	0.1	560	249	5	6	1	1	1.6	3.0	11	0.01
KL44-04	377.8	380.1	0.0043		43	0.16	2.2	6200	750	35	6	2	1	12.8	4.1	11	0.97
KL44-04	380.1	383.2	0.0198		198	0.03	0.1	359	67	5	10	1	1	0.9	2.3	14	0.01
KL44-04	383.2	386.4	0.002		20	0.01	0.7	760	271	4	8	4	1	1.2	3.8	17	0.01
KL44-04	386.4	389.2	0.0028		28	0.01	0.1	195	145	3	4	1	1	1.4	2.1	14	0.01
KL44-04	389.2	392.3	0.0018		18	0.01	0.1	121	67	2	4	0.01	1	0.6	1.5	13	0.01
KL44-04	392.3	395.1	0.0014		14	0.01	0.1	170	76	1	4	2	1	1.7	1.8	12	0.01
KL44-04	395.1	398	0.0137		137	0.01	0.9	540	980	44	5	1	1	24	4.7	13	0.01
KL44-04	398	400.6	0.0335		335	0.02	0.1	291	116	37	35	0.01	1	2	1.9	13	0.01
KL44-04	400.6	403.2	0.0192		192	0.03	0.1	610	236	27	7	1	1	3.3	3.5	13	0.01
KL44-04	403.2	406.1	0.02		200	0.05	0.1	1150	400	35	47	0.01	2	15	5.1	15	0.22
KL44-04	406.1	408.3	0.0012		12	0.06	0.1	1300	291	13	4	0.01	2	4.1	4.8	9	0.4
KL44-04	408.3	411.8	0.0008		8	0.01	0.1	413	132	5	3	0.01	1	1.5	1.9	9	0.01
KL44-04	411.8	413	0.0012		12	0.01	0.1	331	113	2	5	0.01	1	1.3	1.5	9	0.01
KL44-04	413	415.7	0.0084		84	0.02	0.1	298	123	29	5	0.01	2	2.4	4.2	13	0.01
KL44-04	415.7	418.8	0.149		1490	0.12	0.8	317	119	29	13	0.01	6	1.5	3.6	82	0.01
KL44-04	418.8	420.6	0.09		900	0.05	94	33600	104000	98	14	12	1	90	240.0	22	0.35
KL44-04	420.6	423.4	0.0336		336	0.02	1.6	1220	790	67	13	14	1	68	5.6	15	0.2
KL44-04	423.4	425.6	0.0051		51	0.02	1.6	470	510	24	31	43	1	7.9	8.9	12	0.15
KL44-04	425.6	428.4	0.0254		254	0.05	4	8300	5400	25	6	5	1	24	12.2	9	1.27
KL44-04	428.4	431.5	0.0086		86	0.03	1.2	391	266	25	18	20	1	26	4.5	15	0.16
KL44-04	431.5	434.2	0.079		790	0.1	0.6	440	165	18	4	1	1	17.9	3.0	8	0.21
KL44-04	434.2	437.3	0.0168		168	0.01	0.6	500	160	8	8	1	1	15.2	9.8	14	0.13
KL44-04	437.3	440.6	0.0087		87	0.02	0.8	650	340	26	12	2	1	7.3	4.8	15	0.01
KL44-04	440.6	442.6	0.065		650	0.07	0.1	255	81	15	6	0.01	1	0.9	3.8	8	0.01
KL44-04	442.6	445.6	0.418		4180	0.6	2	222	58	24	9	1	9	2.1	7.8	24	0.01
KL44-04	445.6	448.6	0.335		3350	0.43	1.5	232	65	26	15	1	12	1.5	8.3	24	0.01
KL44-04	448.6	451	0.0097		97	0.02	0.1	167	32	17	26	0.01	1	2.3	1.0	11	0.01
KL44-04	451	453.6	0.0248		248	0.08	0.6	980	117	62	1320	1	3	24	3.0	59	0.13
KL44-04	453.6	455.6	0.0213		213	0.13	0.1	740	126	23	1180	4	4	2.2	4.1	40	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL44-04	455.6	458	0.046	460	0.1	0.1	316	67	30	1160	4	8	2	2.8	100	0.01
KL44-04	458	460.1	0.0297	297	0.1	0.5	1250	160	220	1830	3	9	3.9	3.0	122	0.01
KL44-04	460.1	461.6	0.0304	304	0.19	1.4	7400	247	280	2200	3	15	5.7	7.3	60	0.01
KL44-04	461.6	464.6	0.107	1070	0.23	8.7	3960	1220	200	870	20	17	6.8	16.3	88	0.16
KL44-04	464.6	467.6	0.181	1810	0.27	1.3	3760	301	380	37	0.01	8	5.4	5.5	20	0.01
KL44-04	467.6	470.6	0.468	4680	0.34	2.3	6400	2660	520	26	2	10	10.8	9.0	36	0.01
KL44-04	470.6	473.6	0.0056	56	0.02	0.1	232	97	21	12	1	1	1.3	3.0	14	0.01
KL44-04	473.6	476.6	1.01	10100	0.55	3.5	1240	340	170	24	3	12	4.1	12.8	26	0.01
KL44-04	476.6	479.3	0.462	4620	0.27	2	690	150	81	14	2	7	3.1	5.8	17	0.01
KL44-04	479.3	481.6	0.116	1160	0.08	0.1	201	43	24	5	1	4	0.8	2.3	10	0.01
KL44-04	481.6	484.7	0.28	2800	0.21	0.9	256	28	19	5	3	13	0.8	6.0	25	0.01
KL44-04	484.7	487.8	0.22	2200	0.17	1.3	387	107	9	7	1	4	1	6.0	17	0.01
KL44-04	487.8	490.9	0.139	1390	0.07	0.9	295	187	14	4	2	2	0.8	3.8	21	0.01
KL44-04	490.9	492	0.06	600	0.08	0.1	110	19	9	3	1	2	0.4	2.8	12	0.01
KL44-04	492	494.6	0.054	540	0.04	0.1	198	32	10	3	2	1	0.3	5.3	11	0.01
KL44-04	494.6	497.6	0.408	4080	0.31	2.6	980	26	20	2	4	18	0.3	10.5	19	0.01
KL44-04	497.6	500.6	0.23	2300	0.32	1.3	1150	49	24	3	2	3	1.7	4.5	13	0.01
KL44-04	500.6	503.6	0.99	9900	0.49	2.2	118	107	110	9	3	6	3.6	9.5	86	0.01
KL44-04	503.6	505.4	0.153	1530	0.1	0.6	158	30	9	231	1	6	6.9	2.9	13	0.01
KL44-04	505.4	507.6	0.22	2200	0.13	1.2	170	32	17	980	1	5	1.1	3.3	32	0.01
KL44-04	507.6	509.6	1.02	10200	0.56	1.8	248	43	16	156	1	8	1.4	10.0	17	0.01
KL44-04	509.6	512.6	0.081	810	0.07	0.1	138	52	9	62	1	2	1.6	2.0	8	0.01
KL44-04	512.6	515.6	0.069	690	0.04	0.1	93	34	5	326	2	3	1	1.8	19	0.01
KL44-04	515.6	518.6	0.142	1420	0.18	1.1	730	560	18	27	3	3	7.3	5.1	21	0.16
KL44-04	518.6	521.6	0.185	1850	0.14	1.1	610	67	37	37	2	6	3.5	3.8	14	0.01
KL44-04	521.6	524.6	0.151	1510	0.11	1.9	267	67	31	14	3	1	7.8	2.8	10	0.01
KL44-04	524.6	527.4	0.164	1640	0.1	1.1	220	34	16	6	7	1	2.2	2.5	7	0.01
KL44-04	527.4	530.5	0.124	1240	0.15	7.4	430	2000	26	5	4	7	6.3	3.5	12	0.01
KL44-04	530.5	533.6	1.55	15500	1.62	2.5	281	490	32	18	2	10	2.6	12.0	36	0.01
KL44-04	533.6	536.6	0.33	3300	0.34	2.4	1040	171	20	13	4	6	1.1	7.0	19	0.01
KL44-04	536.6	539.6	0.36	3600	0.25	1.1	244	13	24	5	1	8	0.3	5.5	13	0.01
KL44-04	539.6	542.6	0.23	2300	0.09	1.6	391	170	22	5	2	6	2.6	8.5	12	0.01
KL44-04	542.6	545.6	0.137	1370	0.1	0.8	326	105	64	6	4	2	3.5	10.3	16	0.01
KL44-04	545.6	548.6	0.287	2870	0.2	2.7	460	160	34	3	1	5	3.8	9.8	13	0.01
KL44-04	548.6	551.6	0.88	8800	0.73	21.2	9050	7000	70	4	2	6	17.9	16.5	27	0.1
KL44-04	551.6	553.7	0.71	7100	0.82	2.1	4010	900	950	38	5	11	11.2	9.6	51	0.01
KL44-04	553.7	556.3	0.6	6000	0.45	2.3	1330	570	44	4	1	11	4.6	14.3	15	0.01
KL44-04	556.3	559.4	1.88	18800	1.04	3.7	3580	960	20	13	1	18	3.5	15.5	19	0.01
KL44-04	559.4	562.5	1.7	17000	0.74	2.1	630	267	31	40	0.01	18	2.5	13.5	34	0.01
KL44-04	562.5	565.5	0.073	730	0.64	14.3	1550	9900	37	12	4	1	12.8	8.5	24	0.01
KL44-04	565.5	568.7	2.79	27900	1.5	3.2	720	131	43	8	1	22	1.6	25.0	27	0.01
KL44-04	568.7	570.5	2.08	20800	1.18	4.8	321	75	32	6	3	14	1.6	21.0	51	0.01
KL44-04	570.5	572	1.52	15200	2.02	4.5	401	94	18	5	12	22	1.2	21.5	29	0.01
KL44-04	572	574.6	2.75	27500	2.13	5.2	426	240	52	4	3	36	3.8	27.0	45	0.01
KL44-04	574.6	575.6	0.25	2500	0.21	2.7	125	63	23	14	0.01	9	2.4	7.3	68	0.01
KL44-04	575.6	578.6	0.23	2300	0.14	1.8	570	216	73	21	0.01	6	2.1	7.6	54	0.01
KL44-04	578.6	579.8	0.162	1620	0.09	0.8	291	104	38	296	0.01	6	1.9	10.8	75	0.01
KL44-04	579.8	581.3	0.25	2500	0.14	0.8	158	52	32	8	0.01	7	0.8	8.0	75	0.01
KL44-04	581.3	582.8	0.22	2200	0.21	1.5	490	162	41	6	1	8	2.2	10.6	22	0.01
KL44-04	582.8	584.6	0.362	3620	0.14	1.3	144	83	11	52	0.01	11	0.8	3.4	69	0.01
KL44-04	584.6	587.6	0.495	4950	0.15	1.8	234	154	11	44	1	6	0.6	5.8	64	0.01
KL44-04	587.6	590.6	0.31	3100	0.28	2.1	1060	830	35	16	0.01	2	1	6.0	48	0.01
KL44-04	590.6	593.6	0.27	2700	0.43	1.6	185	115	28	10	0.01	7	1.5	4.0	77	0.01
KL44-04	593.6	596.6	2.35	23500	2.44	4.8	255	40	14	23	1	5	1.2	10.5	75	0.01
KL44-04	596.6	599.6	0.49	4900	0.51	9.8	1820	630	53	18	1	7	6.8	4.3	43	0.13
KL44-04	599.6	602.6	0.086	860	0.15	3.7	2190	1400	40	16	3	2	6.5	4.0	24	0.01
KL44-04	602.6	605.6	0.141	1410	0.25	1.1	283	139	38	8	0.01	6	1.5	2.8	72	0.01
KL44-04	605.6	608.6	0.192	1920	0.2	1.4	94	62	10	8	0.01	6	1.1	2.3	65	0.01
KL44-04	608.6	611.6	0.39	3900	0.51	2.1	268	92	28	9	1	14	0.8	5.1	61	0.01
KL44-04	611.6	614.6	0.546	5460	0.53	1.5	45	13	8	21	0.01	8	0.2	2.5	76	0.01
KL44-04	614.6	617.6	0.25	2500	0.33	0.9	91	28	9	6	0.01	5	0.5	2.5	62	0.01
KL44-04	617.6	620.6	0.78	7800	0.51	3	410	237	7	7	3	7	5.6	6.8	74	0.01
KL44-04	620.6	623.6	0.66	6600	0.76	1.3	60	20	6	3	1	8	0.7	5.3	78	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL44-04	623.6	626.6	0.364	3640	0.35	0.8	92	25	13	7	1	7	0.4	3.5	68	0.01
KL44-04	626.6	629.6	2.75	27500	0.79	23.5	2860	3060	82	8	46	3	42	9.0	66	0.21
KL44-04	629.6	632.6	0.96	9600	0.41	2.5	68	21	8	6	0.01	4	2.2	5.3	88	0.01
KL44-04	632.6	635.6	0.29	2900	0.62	3	273	820	73	10	2	8	2.8	4.8	47	0.01
KL44-04	635.6	638.6	2.74	27400	2.28	5.2	440	232	19	4	2	34	4.2	21.0	57	0.01
KL44-04	638.6	641.6	1.13	11300	0.29	6.5	710	225	26	23	4	5	9.6	8.5	140	1.24
KL44-04	641.6	644.6	1.6	16000	0.17	5.9	85	63	23	11	1	4	3.5	4.0	137	0.01
KL44-04	644.6	647.6	0.56	5600	0.07	1.8	106	78	13	7	2	5	3.5	4.1	170	0.01
KL44-04	647.6	649.7	0.165	1650	0.02	0.8	34	20	29	8	2	3	12.2	3.0	171	0.01
KL44-04	649.7	651.6	0.21	2100	0.02	0.9	176	68	12	13	0.01	5	2	3.0	69	0.01
KL44-04	651.6	653.6	0.169	1690	0.04	2.1	94	74	6	37	1	18	5.9	10.5	121	0.01
KL44-04	653.6	656.6	0.104	1040	0.02	1.8	161	550	4	30	1	12	1	9.4	156	0.01
KL44-04	656.6	659.6	0.146	1460	0.02	1	60	24	12	38	1	6	1	1.0	238	0.01
KL44-04	659.6	662.6	0.291	2910	0.01	2.4	18	21	4	66	12	5	1.1	2.8	52	0.01
KL44-04	662.6	665.6	0.152	1520	0.03	1.3	21	17	4	25	3	2	0.01	1.3	38	0.01
KL44-04	665.6	668.6	0.083	830	0.01	1.3	115	86	6	40	6	2	13.4	1.3	30	0.01
KL44-04	668.6	671.6	0.123	1230	0.02	1.9	18	20	3	150	4	3	0.5	1.8	26	0.01
KL44-04	671.6	674.6	0.105	1050	0.01	1.4	37	20	2	53	3	5	1.5	2.5	42	0.01
KL44-04	674.6	677.6	0.098	980	0.01	1.1	17	18	2	23	2	3	0.7	2.3	40	0.01
KL44-04	677.6	680.6	0.138	1380	0.06	1.8	28	32	3	55	12	2	1.1	1.8	28	0.01
KL44-04	680.6	683.6	0.152	1520	0.04	1.4	38	20	3	49	12	3	2	2.0	31	0.01
KL44-04	683.6	686.6	0.115	1150	0.04	0.8	14	13	1	25	4	2	1.2	3.3	135	0.01
KL44-04	686.6	689.2	0.09	900	0.09	0.6	13	17	10	34	1	2	3.2	1.8	35	0.01
KL44-04	689.2	690.6	0.086	860	0.08	0.1	17	24	53	33	1	3	13.3	1.8	18	0.01
KL44-04	690.6	693.7	0.177	1770	0.12	0.6	143	103	8	32	1	5	3.9	3.3	23	0.01
KL44-04	693.7	695.6	0.135	1350	0.06	0.7	19	18	1	17	2	3	1	1.3	24	0.01
KL44-04	695.6	697.8	0.193	1930	0.07	1	64	45	0.01	32	3	3	0.7	1.5	155	0.01
KL44-04	697.8	700.5	0.134	1340	0.09	0.9	24	16	4	56	3	4	2.1	1.0	185	0.1
KL44-04	700.5	702.8	0.057	570	0.06	0.6	16	26	16	74	0.01	3	5.4	1.8	126	0.01
KL44-04	702.8	705.1	0.0278	278	0.04	0.1	13	17	3	19	0.01	2	1.9	0.0	157	0.01
KL44-04	705.1	706.9	0.061	610	0.04	0.1	34	17	2	16	1	3	1.2	3.3	170	0.01
KL44-04	706.9	709.8	0.073	730	0.04	0.1	22	12	2	430	1	5	1.3	2.8	201	0.01
KL44-04	709.8	712.9	0.051	510	0.01	0.7	16	10	2	30	2	14	1	4.0	141	0.01
KL44-04	712.9	716	0.114	1140	0.02	0.7	17	14	2	60	4	4	1.6	3.0	107	0.01
KL44-04	716	718.4	0.0326	326	0.01	0.5	22	32	5	41	2	4	2.1	15.1	142	0.01
KL44-04	718.4	721.2	0.073	730	0.02	0.6	13	8	41	99	2	2	6.7	1.8	204	0.01
KL44-04	721.2	724.3	0.147	1470	0.04	0.1	10	9	540	187	1	5	35	6.0	183	0.01
KL44-04	724.3	725.6	0.049	490	0.01	0.1	9	8	120	61	1	3	15.4	3.5	206	0.01
KL44-04	725.6	728.6	0.0316	316	0.02	0.1	10	7	71	57	1	3	8.3	3.8	201	0.01
KL44-04	728.6	730.8	0.082	820	0.05	0.1	12	11	230	117	1	5	19.1	4.3	174	0.01
KL44-04	730.8	733.8	0.056	560	0.02	0.1	17	11	110	29	0.01	6	11	3.3	123	0.01
KL44-04	733.8	735.5	0.0178	178	0.01	0.1	19	8	26	25	0.01	4	4	3.0	127	0.01
KL44-04	735.5	737	0.0321	321	0.03	0.1	16	7	8	30	0.01	5	2	2.5	81	0.01
KL44-04	737	738.9	0.077	770	0.04	0.1	23	14	14	41	1	1	3.4	2.3	115	0.01
KL44-04	738.9	741.3	0.0314	314	0.02	0.1	15	13	66	24	0.01	1	6.5	1.8	128	0.01
KL44-04	741.3	743.2	0.104	1040	0.04	0.1	21	14	110	66	1	1	14.9	2.5	95	0.01
KL44-04	743.2	745.3	0.118	1180	0.02	1	23	13	5	58	3	1	1.4	2.8	130	0.01
KL44-04	745.3	747.8	0.0326	326	0.02	0.1	152	136	79	121	0.01	3	4.1	4.3	112	0.01
KL44-04	747.8	750.9	0.0279	279	0.01	0.1	58	42	40	55	0.01	1	1.6	3.5	174	0.01
KL44-04	750.9	752.6	0.073	730	0.03	0.1	11	10	6	34	1	2	1.6	2.8	94	0.01
KL44-04	752.6	755.6	0.052	520	0.03	0.1	16	14	11	22	1	3	3.5	4.5	95	0.01
KL44-04	755.6	758.6	0.124	1240	0.05	0.1	10	8	24	19	1	2	4.8	3.5	177	0.01
KL44-04	758.6	761.6	0.083	830	0.03	0.5	23	18	40	38	1	1	6.6	1.8	144	0.01
KL44-04	761.6	764.6	0.0376	376	0.02	0.1	9	8	17	29	1	1	2.6	1.0	109	0.01
KL44-04	764.6	767.6	0.0205	205	0.02	0.1	5	7	39	46	1	1	5.6	1.8	97	0.01
KL44-04	767.6	955.6														
KL44-05	0	1.6	0.0084	84	0.06	8.3	3060	470	22	1	0.01	1	3	2.0	18	0.18
KL44-05	1.6	4.6	0.0025	25	0.09	3.5	870	178	22	1	0.01	1	2.2	1.2	19	0.1
KL44-05	4.6	7.6	0.0069	69	0.01	0.1	67	29	6	1	0.01	1	0.3	0.6	19	0.01
KL44-05	7.6	10.6	0.0036	36	0.01	0.1	37	41	5	2	0.01	1	0.01	0.0	23	0.01
KL44-05	10.6	13.6	0.0016	16	0.01	0.8	89	59	6	2	0.01	1	0.2	1.5	17	0.01
KL44-05	13.6	16.6	0.002	20	0.03	1	114	77	9	3	0.01	1	0.3	1.8	16	0.01
KL44-05	16.6	18.6	0.0026	26	0.02	0.1	72	49	7	2	0.01	1	0.2	1.3	15	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL44-05	18.6	20.1	0.0003		3	0.03	0.9	104	41	10	1	0.01	1	0.5	1.2	13	0.01
KL44-05	20.1	22.3	0.0008		8	0.01	0.1	66	28	7	1	0.01	1	0.2	0.6	12	0.01
KL44-05	22.3	25.4	0.001		10	0.01	0.8	68	39	17	1	0.01	1	0.4	0.9	14	0.01
KL44-05	25.4	28.6	0.0014		14	0.01	1	73	40	18	1	0.01	2	0.4	1.4	13	0.01
KL44-05	28.6	31.8	0.0007		7	0.01	2.9	290	142	7	1	0.01	1	0.7	2.0	12	0.01
KL44-05	31.8	34.6	0.002		20	0.01	2.4	440	132	7	1	0.01	1	0.9	1.7	13	0.01
KL44-05	34.6	37	0.0007		7	0.01	0.9	145	88	10	2	0.01	1	0.8	1.6	14	0.01
KL44-05	37	38.3	0.0006		6	0.02	1.3	175	83	6	1	0.01	1	0.6	1.5	16	0.01
KL44-05	38.3	40.5	0.0007		7	0.01	1.1	151	115	5	1	0.01	1	0.5	1.7	15	0.01
KL44-05	40.5	43.6	0.0003		3	0.01	0.8	152	112	6	1	0.01	1	0.6	1.3	17	0.01
KL44-05	43.6	46.6	0.0009		9	0.01	0.8	203	170	8	2	0.01	1	0.7	1.6	17	0.01
KL44-05	46.6	49.6	0.001		10	0.07	3.4	650	1180	10	1	0.01	1	2.8	4.5	21	0.01
KL44-05	49.6	51.9	0.0016		16	0.04	1.9	276	317	13	2	0.01	1	1.3	1.9	18	0.01
KL44-05	51.9	55	0.0003		3	0.01	1	153	124	6	1	0.01	1	0.6	1.0	17	0.01
KL44-05	55	58.1	0.0054		54	0.17	6.3	1020	680	61	3	7	2	6.4	4.2	19	0.12
KL44-05	58.1	60.6	0.0101		101	0.24	7.8	1380	830	140	3	4	3	9.6	5.9	22	0.15
KL44-05	60.6	63.5	0.0006		6	0.02	3.3	316	118	10	1	2	1	0.8	3.3	20	0.01
KL44-05	63.5	66.6	0.002		20	0.05	4.5	490	480	17	1	1	1	2.1	3.8	21	0.01
KL44-05	66.6	69.7	0.0049		49	0.08	33	4500	10200	28	2	0.01	1	40	33.5	19	0.01
KL44-05	69.7	72.8	0.002		20	0.03	14.1	1560	1100	28	1	0.01	2	4.5	16.2	20	0.01
KL44-05	72.8	75.9	0.0152		152	0.05	3	264	92	8	3	0.01	1	0.7	1.6	15	0.01
KL44-05	75.9	79	0.001		10	0.01	1.9	168	117	20	2	0.01	1	0.5	3.1	19	0.01
KL44-05	79	82.1	0.0011		11	0.09	4.8	570	386	25	1	0.01	1	2.9	4.6	16	0.12
KL44-05	82.1	85.2	0.0005		5	0.02	1.4	165	76	15	1	0.01	1	1	2.7	17	0.01
KL44-05	85.2	88.3	0.0006		6	0.01	0.7	123	48	8	1	0.01	1	0.5	1.4	15	0.01
KL44-05	88.3	91.4	0.0005		5	0.01	0.5	107	31	5	1	0.01	1	0.01	1.3	19	0.01
KL44-05	91.4	94.6	0.0005		5	0.07	1.5	210	93	12	1	0.01	1	1.1	2.9	17	0.01
KL44-05	94.6	97.6	0.0006		6	0.05	1.9	460	132	7	1	0.01	1	0.8	2.0	14	0.01
KL44-05	97.6	99.5	0.003		30	0.02	1.2	184	95	9	8	0.01	1	0.7	1.1	13	0.01
KL44-05	99.5	101.8	0.0061		61	0.01	0.1	13	12	1	3	0.01	2	0.01	0.0	241	0.01
KL44-05	101.8	103.6	0.0008		8	0.05	1.2	301	76	11	1	0.01	2	0.5	1.6	15	0.01
KL44-05	103.6	106.6	0.0009		9	0.02	1.1	188	87	6	1	0.01	1	1.1	1.6	17	0.01
KL44-05	106.6	109.6	0.0008		8	0.01	0.6	182	63	5	2	0.01	1	0.4	1.0	17	0.01
KL44-05	109.6	111.1	0.0015		15	0.01	0.6	111	58	4	3	0.01	1	0.3	0.7	13	0.01
KL44-05	111.1	113.6	0.0013		13	0.01	0.5	75	31	3	2	0.01	1	0.2	0.5	13	0.01
KL44-05	113.6	116.6	0.0007		7	0.05	1.2	314	116	7	1	0.01	1	1	1.7	17	0.01
KL44-05	116.6	119.6	0.0014		14	0.01	1.2	420	48	4	1	0.01	1	0.2	0.8	17	0.01
KL44-05	119.6	122.8	0.001		10	0.01	0.1	156	41	3	1	0.01	1	0.3	0.7	13	0.01
KL44-05	122.8	124.6	0.001		10	0.01	0.6	174	53	3	1	0.01	1	0.2	0.6	13	0.01
KL44-05	124.6	126.6	0.0106		106	0.01	0.1	136	79	6	1	0.01	2	0.7	1.0	16	0.01
KL44-05	126.6	128.8	0.0012		12	0.03	0.6	184	104	2	1	0.01	1	0.01	0.9	13	0.01
KL44-05	128.8	131.5	0.0007		7	0.02	0.7	152	55	3	1	0.01	1	0.01	0.0	14	0.01
KL44-05	131.5	133.6	0.0011		11	0.06	1.5	330	200	12	1	0.01	1	1.1	0.0	17	0.01
KL44-05	133.6	136.1	0.0007		7	0.03	0.1	118	90	5	1	0.01	1	0.4	0.0	12	0.01
KL44-05	136.1	137.1	0.0031		31	0.09	0.7	339	217	21	1	0.01	1	2.3	2.4	18	0.01
KL44-05	137.1	139.6	0.001		10	0.01	0.6	150	120	4	1	0.01	1	0.6	1.2	18	0.01
KL44-05	139.6	142.6	0.002		20	0.01	0.6	1450	46	5	1	0.01	1	0.3	1.0	14	0.01
KL44-05	142.6	145.6	0.0022		22	0.01	0.1	112	71	3	1	0.01	1	0.4	0.0	18	0.01
KL44-05	145.6	148.6	0.0004		4	0.01	0.6	109	44	2	1	0.01	1	0.01	0.0	18	0.01
KL44-05	148.6	151.6	0.0012		12	0.03	0.8	395	290	4	1	0.01	1	0.9	0.7	24	0.01
KL44-05	151.6	153.6	0.0007		7	0.01	1.4	152	80	2	1	0.01	1	0.3	0.0	13	0.01
KL44-05	153.6	154.9	0.0008		8	0.02	0.8	540	110	3	1	0.01	1	0.4	0.7	14	0.01
KL44-05	154.9	157.6	0.0015		15	0.06	3	1000	345	7	2	0.01	1	1.8	0.8	12	0.01
KL44-05	157.6	160.6	0.0004		4	0.02	0.7	116	62	5	1	0.01	1	0.4	0.7	18	0.01
KL44-05	160.6	163.1	0.0005		5	0.04	0.7	210	57	2	1	0.01	1	0.4	0.0	12	0.01
KL44-05	163.1	166.4	0.0012		12	0.28	1.8	267	76	3	1	0.01	1	1.1	0.0	14	0.01
KL44-05	166.4	168.6	0.0005		5	0.19	1	264	53	10	2	0.01	1	1.1	1.2	15	0.01
KL44-05	168.6	169.8	0.0004		4	0.18	0.8	163	74	9	1	0.01	1	0.5	1.0	10	0.01
KL44-05	169.8	172	0.0004		4	0.09	0.1	162	47	6	1	0.01	1	0.3	0.0	9	0.01
KL44-05	172	173.4	0.0005		5	0.04	0.1	144	44	7	1	0.01	1	0.2	0.6	10	0.01
KL44-05	173.4	175.6	0.0007		7	0.02	0.1	145	58	6	1	0.01	1	0.2	0.0	11	0.01
KL44-05	175.6	178.1	0.0008		8	0.01	0.1	115	50	8	2	0.01	1	0.2	0.0	16	0.01
KL44-05	178.1	181.1	0.002		20	0.01	0.1	100	45	7	2	0.01	1	1.1	0.6	16	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL44-05	405.1	406.5														
KL44-05	406.5	409.5														
KL44-05	409.5	411														
KL44-05	411	414.1														
KL44-05	414.1	416.7														
KL44-05	416.7	418.6														
KL44-05	418.6	421.6														
KL44-05	421.6	424.6														
KL44-05	424.6	427.6														
KL44-05	427.6	430.6														
KL44-05	430.6	432														
KL44-05	432	434.9														
KL44-05	434.9	436.6														
KL44-05	436.6	439.6														
KL44-05	439.6	442.6														
KL44-05	442.6	445.6														
KL44-05	445.6	448.6														
KL44-05	448.6	451														
KL44-05	451	454.6														
KL44-05	454.6	457														
KL44-05	457	460														
KL44-05	460	463														
KL44-05	463	466.3														
KL44-05	466.3	469.4														
KL44-05	469.4	472.5														
KL44-05	472.5	475.6														
KL44-05	475.6	478.6														
KL44-05	478.6	481.6														
KL44-05	481.6	484.6														
KL44-05	484.6	487.6														
KL44-05	487.6	489.8														
KL44-05	489.8	492.5														
KL44-05	492.5	495.5														
KL44-05	495.5	497.5														
KL44-05	497.5	499.1														
KL44-05	499.1	502.2														
KL44-05	502.2	505.3														
KL44-05	505.3	508.4														
KL44-05	508.4	511.5														
KL44-05	511.5	514.6														
KL44-05	514.6	517.6														
KL44-05	517.6	520.6														
KL44-05	520.6	523.6														
KL44-05	523.6	525.7														
KL44-05	525.7	526.1														
KL44-05	526.1	529.6														
KL44-05	529.6	532														
KL44-05	532	534.2														
KL44-05	534.2	535.6														
KL44-05	535.6	537.2														
KL44-05	537.2	539.1														
KL44-05	539.1	541.3														
KL44-05	541.3	544.4														
KL44-05	544.4	547.5														
KL44-05	547.5	550.6														
KL44-05	550.6	553.6														
KL44-05	553.6	556.6	0.438	4380	0.43	1.4	292	116	1270	48	2	8	138	8.3	137	0.12
KL44-05	556.6	559.6	0.78	7800	0.49	2.8	1480	805	1520	208	5	9	70	7.2	139	0.39
KL44-05	559.6	562.2	0.59	5900	0.35	2.8	255	211	800	80	5	5	148	8.1	88	0.2
KL44-05	562.2	563.9	0.63	6300	0.51	3.6	960	835	530	70	2	9	24	8.5	113	0.26
KL44-05	563.9	565.6	0.489	4890	0.58	1.2	810	394	95	52	2	11	2.8	8.0	48	0.1
KL44-05	565.6	568.6	0.307	3070	0.85	2.8	1790	533	58	82	3	8	2.9	7.6	36	0.13
KL44-05	568.6	571.6	0.303	3030	0.91	1.4	1740	506	25	225	2	6	1.3	6.8	38	0.1

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL44-05	571.6	574.6	0.349		3490	1.89	1.8	1310	481	41	218	3	7	1.1	6.4	40	0.1
KL44-05	574.6	577.6	0.354		3540	1.79	1.2	550	183	50	70	2	16	1.6	9.4	46	0.01
KL44-05	577.6	580.6	0.208		2080	1.85	0.5	155	30	45	143	1	8	2.8	8.8	93	0.01
KL44-05	580.6	583.3	0.0349		349	0.17	0.1	148	14	15	11	0.01	19	0.5	2.5	35	0.01
KL44-05	583.3	586.4	0.129		1290	0.15	0.1	122	23	13	14	0.01	24	0.3	1.8	31	0.01
KL44-05	586.4	588.7	0.0254		254	0.32	0.1	169	22	42	3	0.01	22	0.8	1.0	28	0.01
KL44-05	588.7	591.8	0.0198		198	0.5	0.1	102	15	14	2	0.01	23	0.4	0.8	22	0.01
KL44-05	591.8	594.9	0.0155		155	0.04	0.1	111	12	5	2	0.01	22	0.01	0.0	23	0.01
KL44-05	594.9	598	0.0259		259	0.1	0.1	115	20	10	4	0.01	24	0.01	0.0	21	0.01
KL44-05	598	601.1	0.0156		156	0.06	0.1	105	11	10	1	0.01	22	0.01	0.0	29	0.01
KL44-05	601.1	604.2	0.05		500	0.14	0.1	102	13	2	6	0.01	19	0.2	1.0	35	0.01
KL44-05	604.2	605.6	0.015		150	0.02	0.1	98	12	5	3	0.01	19	0.2	0.0	27	0.01
KL44-05	605.6	607.9	0.21		2100	0.82	1.1	201	20	38	10	0.01	14	1.5	3.0	46	0.01
KL44-05	607.9	610.6	1.16		11600	3.37	6.3	380	16	30	30	14	19	9.1	17.0	62	0.01
KL44-05	610.6	613.6	1.32		13200	1.56	5.5	520	62	43	9	9	18	4.5	14.2	58	0.1
KL44-05	613.6	616.6	1.19		11900	0.99	5.4	570	19	26	4	20	16	2.3	9.0	28	0.01
KL44-05	616.6	619.6	2.06		20600	3.35	5	1140	12	10	6	20	24	5.6	11.6	67	0.12
KL44-05	619.6	622.6	2.29		22900	3.67	5.9	1040	16	11	5	20	25	3.6	14.0	67	0.1
KL44-05	622.6	625.6	1.58		15800	2.92	2.9	116	80	15	2	3	16	4.1	15.0	45	0.01
KL44-05	625.6	628.6	1.18		11800	0.44	1.3	112	47	11	7	2	14	1.2	17.0	52	0.01
KL44-05	628.6	630.4	0.8		8000	0.28	3.2	108	49	94	3	30	11	60	18.7	47	0.1
KL44-05	630.4	632.4	1.72		17200	0.56	8.1	98	63	160	55	6	8	40	16.7	110	0.2
KL44-05	632.4	634.6	0.157		1570	0.11	1.1	75	60	52	113	4	11	6.3	16.0	84	0.01
KL44-05	634.6	636.6	0.047		470	0.13	0.8	26	28	25	11	3	9	4.5	14.5	59	0.01
KL44-05	636.6	637.6	0.163		1630	0.37	1.3	268	87	34	660	4	31	4.3	16.3	182	0.1
KL44-05	637.6	640.2	0.089		890	0.04	0.1	70	31	25	158	2	32	2.8	18.6	115	0.01
KL44-05	640.2	643.3	0.197		1970	0.07	1.2	103	45	51	123	5	24	10.3	19.2	116	0.01
KL44-05	643.3	646.4	0.205		2050	0.04	2.1	365	108	25	42	4	6	2.2	4.8	105	0.11
KL44-05	646.4	648.9	0.33		3300	0.13	5.5	9400	360	230	29	7	4	4.8	6.8	85	1.4
KL44-05	648.9	651	0.244		2440	0.01	1.2	32	21	13	41	0.01	3	1.4	3.5	135	0.01
KL44-05	651	654.8	0.312		3120	0.09	1.4	197	57	20	38	3	5	1.7	9.8	112	0.01
KL44-05	654.8	656	0.264		2640	0.07	0.7	67	18	30	113	4	5	4.1	8.0	110	0.01
KL44-05	656	659.9	0.351		3510	0.06	1.7	140	67	26	82	2	4	5	6.5	163	0.01
KL44-05	659.9	663	0.245		2450	0.03	1.3	510	105	25	120	2	3	1.5	4.3	154	0.1
KL44-05	663	664.3	0.185		1850	0.05	3.8	285	378	190	770	2	5	9.5	6.2	134	0.18
KL44-05	664.3	667.4	0.249		2490	0.04	1.3	217	82	100	49	2	5	13.6	5.0	68	0.01
KL44-05	667.4	670.5	0.304		3040	0.05	0.1	157	83	18	49	0.01	2	0.9	2.8	107	0.01
KL44-05	670.5	673.1	0.229		2290	0.03	1	600	120	55	86	1	4	3.8	3.5	145	0.01
KL44-05	673.1	675.1	0.185		1850	0.01	0.7	115	67	15	148	0.01	3	1.2	2.9	192	0.01
KL44-05	675.1	678.3	0.136		1360	0.01	0.1	130	128	16	67	1	12	2.1	7.0	149	0.01
KL44-05	678.3	680.9	0.145		1450	0.01	0.6	316	194	42	37	1	1	1.6	3.2	98	0.01
KL44-05	680.9	683.6	0.161		1610	0.01	0.7	233	172	27	30	0.01	2	0.6	1.9	122	0.01
KL44-05	683.6	685.6	0.18		1800	0.02	0.9	95	96	65	119	3	8	5.1	8.0	170	0.01
KL44-05	685.6	688.6	0.149		1490	0.01	0.9	147	163	22	62	0.01	2	1.7	1.8	87	0.01
KL44-05	688.6	690.3	0.115		1150	0.01	0.5	32	22	9	53	1	4	0.8	2.3	114	0.01
KL44-05	690.3	692.1	0.31		3100	0.13	1.7	7000	2020	74	33	1	2	3	3.0	102	0.22
KL44-05	692.1	694.6	0.113		1130	0.01	0.7	57	40	39	73	2	7	2	3.2	137	0.01
KL44-05	694.6	697.6	0.183		1830	0.02	1.9	84	36	160	180	2	8	15.7	2.9	154	0.01
KL44-05	697.6	700.6	0.139		1390	0.01	0.6	135	46	110	184	4	9	18.8	3.8	190	0.01
KL44-05	700.6	703.6	0.0235		235	0.02	0.1	35	20	23	135	1	5	2.4	2.0	215	0.01
KL44-05	703.6	706.1	0.0259		259	0.04	0.1	40	52	26	155	2	4	1.8	3.7	112	0.01
KL44-05	706.1	709.2	0.192		1920	0.02	3.8	278	96	340	85	5	8	7.0	4.2	140	0.12
KL44-05	709.2	712.3	0.102		1020	0.01	1.9	275	126	47	94	4	6	3.5	3.6	149	0.1
KL44-05	712.3	715.4	0.121		1210	0.01	1.1	97	57	67	132	2	3	7.4	2.9	110	0.01
KL44-05	715.4	718.5	0.05		500	0.03	0.5	48	24	13	169	1	7	2.9	7.9	140	0.01
KL44-05	718.5	720.8	0.012		120	0.01	0.1	60	10	6	75	0.01	10	0.9	5.1	128	0.01
KL44-05	720.8	722.6	0.0365		365	0.03	0.1	49	18	17	58	0.01	4	3.1	4.0	148	0.01
KL44-05	722.6	724.2	0.0073		73	0.01	0.1	16	6	7	96	0.01	6	2.8	3.8	157	0.01
KL44-05	724.2	726.2	0.013		130	0.02	0.1	19	13	13	230	2	6	3	12.0	145	0.01
KL44-05	726.2	728.8	0.0244		244	0.04	0.1	440	38	24	267	1	6	1.4	6.5	112	0.12
KL44-05	728.8	730.6	0.0253		253	0.01	0.1	358	117	9	61	0.01	3	1	2.1	179	0.01
KL44-05	730.6	733.6	0.0062		62	0.01	0.1	23	8	3	68	0.01	3	0.5	2.3	116	0.01
KL44-05	733.6	735.6	0.0231		231	0.02	0.1	25	10	15	88	1	5	1.8	4.5	176	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL44-05	735.6	736.6	0.0148	148	0.02	0.1	16	11	6	67	1	6	0.9	3.1	240	0.01
KL44-05	736.6	739.6	0.104	1040	0.01	0.1	29	16	7	117	0.01	3	0.7	2.3	191	0.01
KL44-05	739.6	741.6	0.103	1030	0.01	0.5	58	25	32	138	1	2	3.2	2.7	174	0.01
KL44-05	741.6	743.3	0.154	1540	0.01	0.1	40	18	13	66	0.01	2	1.4	2.8	170	0.01
KL44-05	743.3	745	0.447	4470	0.21	1.2	634	87	53	258	1	8	4	3.5	209	0.01
KL44-05	745	747.1	0.134	1340	0.02	0.9	35	19	42	165	1	3	3.7	2.8	133	0.01
KL44-05	747.1	748.6	0.316	3160	0.02	1.1	112	44	230	197	1	5	13.8	2.1	101	0.01
KL44-05	748.6	751.6	0.282	2820	0.04	0.8	54	28	54	211	2	7	6.1	5.5	93	0.01
KL44-05	751.6	754.6	0.305	3050	0.02	0.7	68	44	11	186	1	4	1	2.7	126	0.01
KL44-05	754.6	757.6	0.264	2640	0.03	0.8	106	37	12	112	2	3	0.8	4.4	162	0.01
KL44-05	757.6	760.2	0.059	590	0.02	0.1	45	17	14	1240	0.01	6	0.6	12.5	201	0.01
KL44-05	760.2	763.3	0.27	2700	0.04	0.5	59	28	32	172	0.01	3	0.6	3.1	163	0.01
KL44-05	763.3	766.1	0.097	970	0.02	0.1	26	14	29	337	0.01	4	1	4.6	139	0.01
KL44-05	766.1	767.1	0.331	3310	0.03	0.7	40	22	440	450	3	1	4.1	2.5	143	0.01
KL44-05	767.1	769.6	0.139	1390	0.01	0.6	120	46	25	185	1	4	1.3	2.5	152	0.01
KL44-05	769.6	772.6	0.046	460	0.01	0.1	53	38	6	158	0.01	8	0.7	13.7	145	0.01
KL44-05	772.6	775.6	0.26	2600	0.02	0.7	30	14	9	213	1	4	0.9	3.8	138	0.01
KL44-05	775.6	778.6	0.0117	117	0.01	0.6	19	10	3	233	0.01	6	0.4	5.6	145	0.01
KL44-06	0	2.7	0.0027	27	0.01	0.8	45	28	10	4	0.01	1	0.5	0.0	16	0.01
KL44-06	2.7	5.7	0.0011	11	0.01	0.7	85	38	10	4	0.01	1	0.4	0.6	18	0.01
KL44-06	5.7	8.3	0.0069	69	0.06	1.2	204	89	16	5	0.01	1	1.2	1.3	24	0.01
KL44-06	8.3	11.4	0.0009	9	0.01	1	200	197	11	3	0.01	1	0.8	1.1	21	0.01
KL44-06	11.4	14.1	0.0012	12	0.04	0.1	98	49	10	2	0.01	1	0.5	0.0	18	0.01
KL44-06	14.1	16.9	0.0011	11	0.03	0.7	89	66	18	3	0.01	1	0.6	0.6	54	0.01
KL44-06	16.9	18.7	0.0007	7	0.02	1.5	151	257	17	2	0.01	1	1.2	1.0	31	0.11
KL44-06	18.7	20.7	0.0013	13	0.01	1.5	84	40	12	9	0.01	1	0.5	0.7	20	0.01
KL44-06	20.7	23.7	0.092	920	0.03	4.9	122	63	27	19	0.01	2	1.1	1.4	18	0.01
KL44-06	23.7	26.2	0.0059	59	0.06	4.4	490	214	29	15	0.01	2	2	4.1	24	0.01
KL44-06	26.2	28.4	0.0009	9	0.01	1.2	63	27	11	3	0.01	2	0.5	0.8	12	0.01
KL44-06	28.4	31.2	0.0006	6	0.01	0.9	80	40	28	3	0.01	1	0.4	1.3	18	0.01
KL44-06	31.2	32.7	0.0006	6	0.01	1.2	48	39	16	3	0.01	1	0.5	0.9	23	0.01
KL44-06	32.7	35.7	0.0005	5	0.01	0.8	33	31	17	5	0.01	2	0.7	0.9	21	0.01
KL44-06	35.7	38.7	0.001	10	0.05	2.8	240	236	18	6	0.01	2	1.9	1.6	18	0.2
KL44-06	38.7	41.7	0.0014	14	0.01	4.7	87	530	12	5	0.01	2	2	0.9	19	0.01
KL44-06	41.7	44.7	0.0018	18	0.05	2.1	184	254	13	9	0.01	2	1.9	1.6	18	0.15
KL44-06	44.7	47.7	0.0008	8	0.01	1	130	89	10	2	0.01	1	0.7	1.4	15	0.14
KL44-06	47.7	50.7	0.0012	12	0.1	1.2	333	140	9	31	0.01	3	1.1	2.7	17	0.28
KL44-06	50.7	53.7	0.0005	5	0.03	1.2	100	91	9	7	0.01	1	2.2	2.4	16	0.2
KL44-06	53.7	56.7	0.001	10	0.01	0.1	42	19	9	6	0.01	1	0.8	0.9	17	0.01
KL44-06	56.7	59.7	0.0004	4	0.01	0.1	31	18	6	3	0.01	2	0.5	1.2	15	0.1
KL44-06	59.7	62.7	0.0006	6	0.02	0.8	80	40	9	7	0.01	1	0.6	1.1	18	0.01
KL44-06	62.7	65.7	0.0008	8	0.04	0.6	50	31	30	5	0.01	1	0.5	0.0	12	0.01
KL44-06	65.7	68.7	0.0012	12	0.17	2.3	261	136	39	7	0.01	1	1.9	1.5	18	0.17
KL44-06	68.7	71.7	0.0017	17	0.05	2.7	1340	2000	42	4	0.01	1	2.8	2.9	25	0.1
KL44-06	71.7	74.7	0.0016	16	0.07	0.6	108	99	56	3	0.01	1	0.9	1.4	20	0.27
KL44-06	74.7	77.7	0.0025	25	0.07	0.7	117	163	26	4	0.01	1	1.1	2.7	20	0.12
KL44-06	77.7	80.7	0.0009	9	0.04	0.1	94	80	24	3	0.01	2	0.9	0.6	18	0.01
KL44-06	80.7	83.7	0.0025	25	0.08	0.6	500	193	43	3	0.01	1	12	2.2	21	0.26
KL44-06	83.7	86.7	0.0036	36	0.03	0.1	82	107	48	2	0.01	1	1.9	1.6	24	0.1
KL44-06	86.7	89.7	0.0023	23	0.01	0.5	93	105	43	5	0.01	1	1.1	0.6	21	0.01
KL44-06	89.7	92.7	0.0228	228	0.01	0.6	290	87	29	10	1	1	0.7	1.2	41	0.01
KL44-06	92.7	95.7	0.051	510	0.04	3	700	325	49	9	9	2	2.6	7.1	33	0.27
KL44-06	95.7	98.7	0.0038	38	1.12	2.4	357	159	150	6	2	1	3.3	6.0	33	0.25
KL44-06	98.7	101.7	0.0007	7	0.01	0.6	123	35	24	3	0.01	2	1.5	0.0	37	0.01
KL44-06	101.7	104.7	0.0014	14	0.01	0.7	93	51	25	2	4	1	1.7	0.8	27	0.01
KL44-06	104.7	107.7	0.0129	129	0.02	1.2	760	309	48	4	2	1	1	2.0	20	0.01
KL44-06	107.7	110.7	0.0033	33	0.04	0.1	115	46	26	4	0.01	2	1.9	0.0	33	0.01
KL44-06	110.7	113.1	0.0046	46	0.01	0.1	82	32	19	25	0.01	1	1.8	0.0	38	0.01
KL44-06	113.1	115.1	0.0021	21	0.03	0.6	115	64	42	12	3	1	1.8	1.0	77	0.01
KL44-06	115.1	116.5	0.047	470	0.03	0.6	690	88	44	18	2	4	2.3	1.4	56	0.01
KL44-06	116.5	118.7	0.0095	95	0.84	2.3	720	259	55	14	1	6	7.2	3.3	49	0.88
KL44-06	118.7	119.7	0.13	1300	0.37	69	58500	50500	180	10	0.01	1	116	52.0	21	4
KL44-06	119.7	122.3	2.32	23200	1.32	243	5400	28300	9800	94	460	4	322	80.0	121	23.8

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL44-06	122.3	123.4	0.158		1580	0.19	6.2	1060	520	520	24	19	4	40	8.3	125	3.08
KL44-06	123.4	125.7	0.081		810	1.17	16.9	3740	2400	430	127	32	4	40	14.0	110	1.77
KL44-06	125.7	128.7	0.0196		196	2.13	3	2300	870	190	24	3	2	12	3.5	45	0.51
KL44-06	128.7	131.2	0.0109		109	0.46	1.4	1880	610	75	24	1	2	4.9	2.3	26	0.28
KL44-06	131.2	133.4	0.0046		46	0.27	1.9	2150	1150	67	29	6	1	5.1	3.3	122	0.24
KL44-06	133.4	134.6	0.0024		24	0.47	2	2300	1230	110	20	2	2	5.6	2.0	102	0.21
KL44-06	134.6	137.2	0.0031		31	0.43	5.9	2640	2180	150	31	39	2	8.6	6.0	189	0.18
KL44-06	137.2	140.4	0.0018		18	0.68	3.7	4100	1140	170	43	7	3	10.7	2.8	118	0.36
KL44-06	140.4	141.7	0.0015		15	0.24	1	2080	600	52	11	0.01	2	3	2.0	189	0.92
KL44-06	141.7	144.7	0.0015		15	0.35	1.9	2570	650	150	26	1	1	11	2.0	95	0.19
KL44-06	144.7	147.2	0.0017		17	0.57	3.8	4910	2540	200	34	1	3	12.7	4.8	123	0.38
KL44-06	147.2	149.3	0.0075		75	0.81	10.3	8410	3500	190	326	2	3	14.2	3.5	104	0.41
KL44-06	149.3	151.2	0.0031		31	1.84	7.2	13800	7000	470	1050	14	2	28	6.2	112	0.57
KL44-06	151.2	152.7	0.004		40	1.63	8.6	21700	7100	470	530	30	4	40	7.5	104	0.75
KL44-06	152.7	155.7	0.0376		376	1.87	6.9	20100	7400	500	2100	46	4	56	23.1	87	1.91
KL44-06	155.7	157.9	0.0211		211	2.52	4.5	12400	5010	520	520	24	5	58	19.0	90	2.42
KL44-06	157.9	159.7	0.0028		28	1.2	1.6	5510	1680	400	366	3	1	32	7.7	98	1
KL44-06	159.7	161.7	0.0107		107	0.84	2.6	5540	2080	250	910	10	2	36	14.5	110	0.76
KL44-06	161.7	164.7	0.065		650	0.3	4.3	4320	1640	280	300	10	5	50	12.0	26	0.17
KL44-06	164.7	166.6	0.0401		401	0.41	3.6	2180	1170	220	211	4	2	46	5.5	26	0.16
KL44-06	166.6	169.4	0.0121		121	0.34	2.8	2730	1930	120	42	8	1	19.9	12.3	30	0.16
KL44-06	169.4	172.1	0.0086		86	0.17	2	2580	1740	54	26	15	1	16.3	8.5	16	0.01
KL44-06	172.1	173.3	0.0156		156	0.03	0.7	950	248	28	21	1	1	4	3.3	16	0.01
KL44-06	173.3	176.5	0.0045		45	0.03	1.2	490	184	31	20	4	1	2.7	1.3	16	0.01
KL44-06	176.5	179.6	0.0056		56	0.06	4	363	510	48	15	72	2	2.4	12.6	17	0.01
KL44-06	179.6	181.8	0.0051		51	0.03	3.5	325	420	35	36	44	4	2.6	4.3	12	0.01
KL44-06	181.8	184.3	0.0076		76	0.07	1.6	540	227	43	39	13	1	7	2.5	19	0.01
KL44-06	184.3	186.9	0.063		630	0.08	3.1	1040	440	240	34	5	3	38	4.5	20	0.01
KL44-06	186.9	190	0.0068		68	0.02	0.8	410	151	30	38	8	4	2.8	2.5	17	0.01
KL44-06	190	191.7	0.0021		21	0.03	1.6	286	259	22	33	17	1	1.5	4.0	19	0.01
KL44-06	191.7	194.3	0.0018		18	0.01	1.2	390	272	18	27	8	2	1.1	3.3	19	0.01
KL44-06	194.3	197.3	0.097		970	0.06	1.8	293	203	41	248	35	3	3.4	3.5	23	0.01
KL44-06	197.3	199.8	0.0132		132	0.07	11.8	1530	1150	47	51	102	1	4.8	21.9	17	0.01
KL44-06	199.8	202.7	0.0053		53	0.02	0.7	480	148	21	57	13	1	2.3	2.6	19	0.01
KL44-06	202.7	205.2	0.0109		109	0.05	5.8	1180	690	32	45	64	1	2.9	12.4	15	0.01
KL44-06	205.2	207.8	0.0272		272	0.22	2.7	1480	840	170	73	30	1	16	7.9	35	0.1
KL44-06	207.8	210.9	0.0057		57	0.02	1.8	450	396	12	54	16	1	2.1	4.0	17	0.01
KL44-06	210.9	213.5	0.0265		265	0.05	2	480	510	73	16	12	1	1.5	4.1	18	0.01
KL44-06	213.5	215.7	0.0068		68	0.02	2.4	400	385	15	14	10	1	1.9	5.3	13	0.01
KL44-06	215.7	218.4	0.0343		343	0.07	1.6	750	520	77	19	8	1	8.2	5.6	16	0.01
KL44-06	218.4	221.6	0.0139		139	0.04	2	700	430	32	18	14	1	6.4	5.7	16	0.01
KL44-06	221.6	224.7	0.0238		238	0.05	2.3	890	1180	61	13	9	1	5.4	6.9	15	0.01
KL44-06	224.7	227.7	0.0117		117	0.03	1.8	680	780	24	15	7	1	3.6	5.5	9	0.01
KL44-06	227.7	228.6	0.0067		67	0.02	1.5	510	380	14	16	9	1	2.1	5.1	10	0.01
KL44-06	228.6	230	0.0258		258	0.05	1.2	820	500	47	14	6	1	4.7	4.4	11	0.01
KL44-06	230	232.4	0.006		60	0.02	0.7	270	198	20	9	4	1	2	1.4	12	0.01
KL44-06	232.4	235.2	0.054		540	0.07	1.4	800	310	200	10	5	1	5	3.1	13	0.01
KL44-06	235.2	238.1	0.0056		56	0.01	1.2	332	188	24	15	6	1	1.7	2.6	12	0.01
KL44-06	238.1	240.5	0.0293		293	0.04	0.9	510	280	73	34	8	1	15	3.7	18	0.01
KL44-06	240.5	243.7	0.0213		213	0.05	1.2	660	314	45	17	6	1	8.9	2.7	12	0.01
KL44-06	243.7	246.3	0.0174		174	0.03	0.7	630	260	39	16	6	1	8.5	2.8	9	0.01
KL44-06	246.3	248.9	0.0075		75	0.01	0.6	398	191	16	19	5	1	4.9	1.9	13	0.01
KL44-06	248.9	251.5	0.0117		117	0.04	1.7	1160	440	18	17	16	1	4.2	6.1	18	0.01
KL44-06	251.5	254.7	0.008		80	0.04	1.2	404	200	37	12	10	1	2	4.7	14	0.01
KL44-06	254.7	257	0.048		480	0.1	0.1	620	309	150	22	6	1	4.7	2.4	20	0.01
KL44-06	257	260	0.24		2400	0.21	1.9	1940	440	540	68	10	4	29	6.8	32	0.13
KL44-06	260	262.6	0.4		4000	0.64	77	38300	64300	1390	193	90	8	120	29.5	54	1.45
KL44-06	262.6	265.1	0.119		1190	0.16	1	1230	710	440	56	7	3	17	5.1	21	0.4
KL44-06	265.1	267	0.253		2530	0.26	2.6	4620	1180	880	93	10	8	22	17.1	45	0.7
KL44-06	267	269.3	0.0076		76	0.04	0.5	680	218	21	20	7	1	1.8	3.4	14	0.01
KL44-06	269.3	272.1	0.0285		285	0.07	0.6	680	192	71	25	7	1	2.5	3.4	15	0.01
KL44-06	272.1	273.8	0.0054		54	0.03	0.5	318	580	17	14	2	1	1.4	1.7	13	0.01
KL44-06	273.8	275.7	0.0069		69	0.03	0.8	580	196	20	31	22	1	1.8	3.2	16	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL44-06	275.7	278.7	0.0121	121	0.03	0.6	690	770	26	14	24	1	1.4	3.9	14	0.01
KL44-06	278.7	281.7	0.0159	159	0.08	0.1	440	100	31	12	1	1	1.1	1.1	16	0.01
KL44-06	281.7	284.7	0.0054	54	0.06	0.1	382	148	24	7	2	1	0.7	1.3	12	0.01
KL44-06	284.7	287.7	0.0138	138	0.12	0.1	680	104	42	12	4	1	2.6	2.9	18	0.25
KL44-06	287.7	290.7	0.0366	366	0.08	0.1	710	97	120	14	2	2	1.5	1.8	22	0.1
KL44-06	290.7	293.7	0.061	610	0.09	0.6	650	97	48	10	1	3	1.3	2.7	18	0.01
KL44-06	293.7	296.7	0.202	2020	0.1	0.7	680	56	33	34	6	1	2.2	3.6	30	0.01
KL44-06	296.7	299.7	0.021	210	0.06	0.1	1120	141	36	12	3	2	2.6	3.8	16	0.01
KL44-06	299.7	302.5	0.0204	204	0.15	1.4	420	91	52	10	0.01	1	4.3	2.3	18	0.15
KL44-06	302.5	305.6	0.024	240	0.32	6.6	1890	770	160	9	2	1	11	5.6	24	0.39
KL44-06	305.6	308.6	0.0274	274	0.23	0.9	960	205	130	13	2	1	6.4	4.6	28	0.01
KL44-06	308.6	311.6	0.148	1480	0.22	0.9	830	210	270	30	3	3	6.1	13.0	29	0.01
KL44-06	311.6	314.7	0.471	4710	0.7	2.5	1040	78	70	9	3	10	2.3	9.0	39	0.01
KL44-06	314.7	317.7	0.59	5900	0.7	2	720	38	44	16	2	13	1.2	7.0	31	0.01
KL44-06	317.7	320.7	0.98	9800	1.66	7.3	1210	79	120	137	20	31	2.5	31.0	24	0.01
KL44-06	320.7	323.7	1.14	11400	1.76	5.3	650	41	110	31	3	27	2	20.5	23	0.01
KL44-06	323.7	326.7	0.6	6000	0.45	1.3	118	31	41	234	7	13	1.3	14.0	28	0.01
KL44-06	326.7	329.7	0.296	2960	0.24	0.8	380	148	88	36	2	10	3.8	5.5	19	0.01
KL44-06	329.7	332.7	0.85	8500	0.37	3.9	6000	750	120	17	2	26	7.3	13.5	40	0.01
KL44-06	332.7	335.7	0.441	4410	0.27	0.8	2100	390	270	640	0.01	14	1.9	14.8	78	0.26
KL44-06	335.7	337.9	0.162	1620	0.16	0.7	2630	420	330	1050	0.01	20	1.4	11.3	76	0.36
KL44-06	337.9	341	0.176	1760	0.27	0.7	2700	570	380	2180	0.01	19	3.7	14.1	102	0.9
KL44-06	341	344	0.386	3860	0.28	1.3	202	48	37	214	0.01	9	1.2	5.3	32	0.01
KL44-06	344	347.2	0.26	2600	0.2	1	165	54	62	730	3	8	1.8	4.8	33	0.01
KL44-06	347.2	348.6	0.113	1130	0.11	0.1	530	84	120	890	0.01	6	3.5	5.0	65	0.01
KL44-06	348.6	350.7	0.0162	162	0.06	0.8	600	176	36	15	4	2	2.8	2.8	10	0.01
KL44-06	350.7	353.7	0.159	1590	0.21	0.6	330	93	96	700	0.01	7	1.5	4.5	99	0.01
KL44-06	353.7	356.3	0.39	3900	0.54	1.3	154	16	60	60	0.01	18	6.8	8.8	21	0.01
KL44-06	356.3	359.1	0.457	4570	0.61	1.6	191	30	71	287	2	18	6	15.2	29	0.01
KL44-06	359.1	362.2	0.31	3100	0.22	1	64	18	12	35	0.01	19	0.3	4.5	20	0.01
KL44-06	362.2	365.3	0.411	4110	0.48	1.5	1120	257	44	294	1	14	2.1	11.5	27	0.01
KL44-06	365.3	367.9	0.63	6300	0.48	1.3	96	19	42	102	0.01	19	0.8	12.3	26	0.01
KL44-06	367.9	371	0.66	6600	0.43	1.9	200	26	31	25	0.01	26	0.9	7.3	30	0.01
KL44-06	371	374.1	0.22	2200	0.09	0.1	55	14	11	35	0.01	6	0.3	4.8	18	0.01
KL44-06	374.1	377.2	0.27	2700	0.19	1.2	71	18	16	2120	2	9	0.5	6.0	18	0.01
KL44-06	377.2	380.3	0.346	3460	0.25	1.3	100	14	11	251	0.01	11	0.5	4.1	14	0.01
KL44-06	380.3	383.4	0.331	3310	0.25	1.4	99	16	13	253	0.01	12	0.3	3.8	11	0.01
KL44-06	383.4	386.5	0.517	5170	0.35	1	97	42	9	19	1	10	0.3	4.5	16	0.01
KL44-06	386.5	389.6	0.54	5400	0.38	0.9	98	46	9	26	1	12	0.4	5.0	14	0.01
KL44-06	389.6	392.7	0.13	1300	0.1	0.7	183	37	13	7	0.01	5	0.5	2.8	19	0.01
KL44-06	392.7	395.7	1.03	10300	0.67	8	2600	60	19	39	1	24	0.9	9.5	16	0.01
KL44-06	395.7	398.7	0.41	4100	0.32	3.4	10900	66	21	54	4	38	0.7	8.5	20	0.01
KL44-06	398.7	401.7	1	10000	0.64	8.5	2500	58	20	43	1	26	1.1	9.8	19	0.01
KL44-06	401.7	404.7	0.84	8400	0.57	2.7	2400	620	450	12	2	10	6.8	9.0	54	0.01
KL44-06	404.7	407.7	0.79	7900	0.55	2	770	194	69	11	4	12	3.3	5.8	32	0.01
KL44-06	407.7	410.7	0.157	1570	0.16	0.1	159	105	51	118	0.01	6	1.8	3.0	30	0.01
KL44-06	410.7	413.1	0.8	8000	0.52	1.9	184	45	18	53	3	14	6.4	9.8	26	0.01
KL44-06	413.1	416.2	1.1	11000	0.74	3.2	460	239	44	640	5	37	7.3	10.0	38	0.01
KL44-06	416.2	419.3	0.82	8200	0.34	1.2	405	158	26	120	0.01	46	1.8	4.6	23	0.01
KL44-06	419.3	422.3	0.73	7300	0.39	3	720	480	36	153	0.01	25	3.4	2.5	13	0.01
KL44-06	422.3	425.4	0.088	880	0.05	3	1560	2760	35	1800	3	5	3.2	3.5	56	0.01
KL44-06	425.4	428	0.202	2020	0.08	2.4	2010	940	26	40	3	18	4.7	3.3	19	0.01
KL44-06	428	429.8	2.04	20400	0.68	8.1	1490	56	8	32	3	52	4.5	6.0	17	0.01
KL44-06	429.8	431.6	1.44	14400	0.43	5.1	4220	65	6	53	1	87	3.2	3.5	18	0.01
KL44-06	431.6	433.4	0.9	9000	0.23	3.2	1510	48	13	8	0.01	54	1.4	3.0	26	0.01
KL44-06	433.4	434.7	1.52	15200	0.47	8.9	2110	1300	15	7	52	57	4	8.0	16	0.01
KL44-06	434.7	437.7	1.38	13800	0.41	17.6	530	158	50	11	32	51	4.4	4.0	20	0.01
KL44-06	437.7	440.7	0.49	4900	0.76	11.2	43100	22600	78	9	11	42	6.7	7.0	28	0.01
KL44-06	440.7	443.7	0.366	3660	0.05	5.7	630	183	27	4	4	60	2.6	1.0	17	0.01
KL44-06	443.7	446.7	0.26	2600	0.14	6.3	830	209	16	5	7	56	2.2	0.8	15	0.01
KL44-06	446.7	449.7	0.499	4990	0.26	4.7	1620	273	40	3	5	58	3.1	6.3	15	0.01
KL44-06	449.7	452.7	1.27	12700	0.94	7.3	610	130	24	6	5	46	2.3	10.0	18	0.01
KL44-06	452.7	455.7	0.94	9400	1.08	7.4	1370	930	23	2	5	38	2.1	7.0	19	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL44-06	455.7	458.7	0.108	1080	0.73	6	620	168	42	3	10	33	2.8	7.9	22	0.01
KL44-06	458.7	461.7	1.76	17600	1.46	15.1	840	169	19	7	60	36	6.1	14.2	23	0.01
KL44-06	461.7	464.7	2.24	22400	1	21	48700	7900	87	4	2	34	5.9	9.0	26	0.01
KL44-06	464.7	467.7	1.79	17900	0.73	5	1010	198	39	15	0.01	19	2.8	8.0	23	0.01
KL44-06	467.7	470.7	1.43	14300	0.47	3.3	500	122	11	37	1	25	1.6	9.5	19	0.01
KL44-06	470.7	473.7	1.76	17600	0.94	4.7	2020	365	8	1	0.01	34	2.1	10.8	19	0.01
KL44-06	473.7	476.7	1.09	10900	0.37	3.4	1070	298	9	11	0.01	33	4	5.5	18	0.01
KL44-06	476.7	479.7	2.47	24700	0.74	5.2	620	338	2	8	1	39	2.3	6.5	19	0.01
KL44-06	479.7	482.7	2.08	20800	0.66	4.2	570	156	1	6	0.01	41	1.7	14.0	19	0.01
KL44-06	482.7	485.7	1.64	16400	0.56	3.2	470	144	7	2	0.01	27	1.9	11.0	22	0.01
KL44-06	485.7	488.7	1.39	13900	0.48	3.7	430	26	0.01	4	2	32	0.5	10.8	16	0.01
KL44-06	488.7	491.7	3.6	36000	1.38	11.2	1440	27	0.01	9	0.01	34	0.7	15.5	16	0.01
KL44-06	491.7	494.7	0.87	8700	0.46	3.7	680	74	3	1	2	28	2	2.8	24	0.01
KL44-06	494.7	497.7	1.19	11900	0.64	7.1	770	80	5	3	5	27	0.8	6.0	28	0.01
KL44-06	497.7	500.7	3.6	36000	1.97	10	890	134	3	17	0.01	21	1.7	18.0	32	0.01
KL44-06	500.7	503.7	1.65	16500	0.98	19.9	500	106	16	94	59	40	1.4	11.5	52	0.01
KL44-06	503.7	506.7	0.63	6300	0.96	10.6	346	174	340	22	160	27	1.9	13.3	51	0.01
KL44-06	506.7	509.7	2.43	24300	4	55	930	348	24	3	160	10	5.6	18.0	30	0.01
KL44-06	509.7	511.2	4.13	41300	6.1	92	315	46	4	6	74	22	2.2	25.5	42	0.01
KL44-06	511.2	512.7	3.01	30100	2.02	48	254	52	33	4	71	108	0.9	20.5	64	0.01
KL44-06	512.7	514.6	2.76	27600	1.44	21.8	79	26	12	6	187	64	0.5	27.5	63	0.01
KL44-06	514.6	516.8	2.5	25000	0.58	14.3	207	100	270	24	72	16	2	17.5	91	1.4
KL44-06	516.8	519.1	2.17	21700	0.84	13.2	101	126	48	302	170	23	0.3	17.0	58	0.01
KL44-06	519.1	521.7	1.8	18000	0.26	6.1	265	640	76	680	1	14	0.4	11.5	77	0.01
KL44-06	521.7	524.1	0.59	5900	0.21	2.1	103	40	20	112	3	12	0.3	8.7	53	0.01
KL44-06	524.1	526.1	1.12	11200	0.32	2.1	63	38	32	59	2	13	0.4	11.8	62	0.01
KL44-06	526.1	527.7	0.89	8900	0.71	4.3	256	140	19	214	9	13	0.5	3.7	61	0.01
KL44-06	527.7	530.7	1.05	10500	0.57	2.6	48	27	21	109	1	12	1.1	11.8	64	0.01
KL44-06	530.7	533.7	1.06	10600	0.55	2.4	43	32	19	106	2	12	1.2	7.5	63	0.01
KL44-06	533.7	536.7	0.48	4800	0.12	1.6	108	46	9	46	1	13	0.7	6.0	156	0.01
KL44-06	536.7	539.7	0.77	7700	0.51	2.5	48	13	1	48	1	13	0.01	7.0	84	0.01
KL44-06	539.7	542.7	0.67	6700	0.35	1.7	60	6	0.01	63	0.01	9	0.01	4.5	75	0.01
KL44-06	542.7	545.7	0.76	7600	0.28	1.8	34	10	2	27	1	8	0.2	6.3	68	0.01
KL44-06	545.7	548.7	0.97	9700	0.46	3.9	202	195	47	31	1	12	30	11.2	72	0.01
KL44-06	548.7	551.7	0.43	4300	0.24	22.6	284	5600	120	22	1	7	380	5.5	69	0.72
KL44-06	551.7	554.7	0.95	9500	0.28	2	49	22	3	16	1	10	0.4	6.8	87	0.01
KL44-06	554.7	557.7	1.36	13600	0.35	3.7	86	25	2	9	1	12	0.01	8.0	88	0.01
KL44-06	557.7	560.7	0.286	2860	0.15	2	37	23	3	76	0.01	5	1.4	2.8	67	0.01
KL44-06	560.7	563.7	0.258	2580	0.11	1.6	26	8	2	36	1	6	0.01	3.0	61	0.01
KL44-06	563.7	566.7	0.28	2800	0.15	1.5	25	9	2	62	0.01	6	0.01	5.4	64	0.01
KL44-06	566.7	569.7	0.448	4480	0.15	2	80	17	2	37	0.01	12	0.01	4.0	86	0.01
KL44-06	569.7	572.7	0.62	6200	0.33	14	89	89	160	22	6	13	260	6.0	74	0.28
KL44-06	572.7	575.7	0.379	3790	0.15	1.1	59	13	4	23	0.01	9	1.6	3.3	76	0.01
KL44-06	575.7	578.7	0.38	3800	0.13	1	53	10	2	10	0.01	11	0.2	4.5	81	0.01
KL44-06	578.7	581.7	0.67	6700	0.19	1.2	58	11	3	6	0.01	14	0.01	3.5	80	0.01
KL44-06	581.7	584.7	0.412	4120	0.13	1	63	9	2	11	0.01	9	0.01	3.5	72	0.01
KL44-06	584.7	587.7	0.92	9200	0.28	2.2	43	31	2	21	1	14	2.2	6.8	75	0.01
KL44-06	587.7	590.7	0.66	6600	0.21	1.4	48	9	2	41	0.01	14	0.3	5.5	76	0.01
KL44-06	590.7	593.7	0.59	5900	0.23	2.1	57	13	6	48	2	9	0.3	5.0	83	0.01
KL44-06	593.7	596.7	0.417	4170	0.15	1.6	73	70	6	64	1	9	0.9	3.5	66	0.01
KL44-06	596.7	599.3	0.34	3400	0.15	1.7	43	18	3	67	1	8	1.6	3.0	54	0.01
KL44-06	599.3	602.3	0.52	5200	0.24	1.3	56	29	4	134	0.01	12	0.3	6.3	85	0.01
KL44-06	602.3	604.5	0.274	2740	0.12	1.6	86	64	8	20	1	6	0.7	1.8	51	0.01
KL44-06	604.5	605.7	0.21	2100	0.12	2.9	85	85	11	16	0.01	5	3.4	3.0	42	0.01
KL44-06	605.7	608.7	0.25	2500	0.14	1.2	201	42	3	31	0.01	6	0.01	2.3	53	0.01
KL44-06	608.7	611.7	0.515	5150	0.23	1.2	61	8	1	18	0.01	6	0.01	4.5	47	0.01
KL44-06	611.7	614.7	1.6	16000	0.53	2.1	346	83	3	1080	0.01	15	0.2	10.0	51	0.01
KL44-06	614.7	617.7	0.412	4120	0.07	1.5	159	52	17	216	1	18	1.3	21.9	135	0.01
KL44-06	617.7	620.7	0.282	2820	0.04	1.1	59	34	23	18	1	6	8.9	4.8	131	0.01
KL44-06	620.7	623.7	0.242	2420	0.02	0.7	28	18	8	155	0.01	7	0.6	5.0	122	0.01
KL44-06	623.7	626.7	0.459	4590	0.06	1.3	47	23	5	65	0.01	4	0.5	6.0	163	0.01
KL44-06	626.7	629.7	0.382	3820	0.03	0.9	72	25	4	34	1	7	0.7	8.5	132	0.01
KL44-06	629.7	632.7	0.226	2260	0.01	0.1	103	45	3	60	0.01	6	0.5	2.8	169	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL44-06	632.7	635.7	1.37	13700	0.4	11.4	500	295	110	56	0.01	16	40	12.3	120	0.33
KL44-06	635.7	638.7	0.57	5700	0.21	2.3	203	171	90	188	0.01	9	14	6.0	95	0.14
KL44-06	638.7	641.7	1.09	10900	0.24	1.6	155	48	8	136	0.01	8	1.2	6.5	102	0.01
KL44-06	641.7	644.7	0.278	2780	0.02	0.1	65	29	6	20	0.01	6	0.3	2.5	139	0.01
KL44-06	644.7	647.7	0.334	3340	0.05	2.8	1570	162	58	67	1	5	11	4.0	74	0.23
KL44-06	647.7	650.7	0.58	5800	0.22	2.4	180	172	100	168	0.01	9	16	7.0	95	0.11
KL44-06	650.7	653.7	0.35	3500	0.12	1.4	44	21	5	52	2	6	0.5	4.3	131	0.01
KL44-06	653.7	656.7	0.445	4450	0.13	1.3	62	25	10	145	2	6	1.2	4.0	101	0.01
KL44-06	656.7	659.7	0.33	3300	0.07	1.5	59	23	8	34	1	5	0.01	2.9	165	0.01
KL44-06	659.7	662.7	0.429	4290	0.19	3.4	191	135	58	54	1	6	5.6	2.8	156	0.01
KL44-06	662.7	665.7	0.471	4710	0.21	1.7	197	71	74	26	1	8	5.1	5.8	110	0.01
KL44-06	665.7	668.7	0.435	4350	0.19	1.4	175	75	61	42	1	7	5	2.8	119	0.14
KL44-06	668.7	671.7	0.488	4880	0.16	2.2	264	87	62	33	0.01	10	18	9.0	157	0.2
KL44-06	671.7	673.8	0.228	2280	0.03	0.7	42	17	2	40	0.01	4	0.01	3.3	121	0.01
KL44-06	673.8	676.9	0.226	2260	0.05	1.3	196	76	64	192	1	12	2.6	5.5	148	0.1
KL44-06	676.9	680	0.22	2200	0.03	1.1	185	79	16	73	0.01	11	1	2.5	120	0.01
KL44-06	680	683.1	0.24	2400	0.02	1.7	225	117	38	26	0.01	8	6.6	2.6	65	0.12
KL44-06	683.1	686.2	0.22	2200	0.21	3.8	168	86	170	136	2	27	18	14.0	64	0.19
KL44-06	686.2	689.3	0.176	1760	0.03	1.5	143	58	21	43	1	10	7.9	4.5	121	0.1
KL44-06	689.3	692.4	0.224	2240	0.05	1.2	188	84	53	37	1	7	8.5	6.5	124	0.12
KL44-06	692.4	695.5	0.21	2100	0.05	1.3	200	96	47	36	1	8	7.1	5.5	121	0.14
KL44-06	695.5	698.5	0.297	2970	0.09	1.2	129	35	31	20	0.01	10	7.5	6.5	112	0.15
KL44-06	698.5	701.6	0.27	2700	0.09	1.1	149	59	19	23	1	16	4.9	7.4	248	0.1
KL44-06	701.6	704.7	0.135	1350	0.03	1	79	36	15	19	0.01	8	3.5	3.8	185	0.01
KL44-06	704.7	707.7	0.22	2200	0.05	1.5	82	43	14	5	0.01	5	8.9	4.1	123	0.01
KL44-06	707.7	710.7	0.125	1250	0.34	1.3	184	510	61	78	4	40	18	7.8	99	0.12
KL44-06	710.7	713.7	0.205	2050	0.02	1.3	172	142	26	16	0.01	16	6.2	3.5	106	0.14
KL44-06	713.7	716.7	0.228	2280	0.01	1	113	64	27	4	0.01	5	10	2.5	148	0.1
KL44-06	716.7	719.7	0.106	1060	0.01	1	157	109	26	27	0.01	4	7.2	1.3	108	0.01
KL44-06	719.7	722.7	0.109	1090	0.01	0.1	163	117	27	27	0.01	6	6.8	2.0	98	0.01
KL44-06	722.7	725.7	0.078	780	0.01	0.1	86	60	9	45	0.01	4	4.5	2.0	121	0.01
KL44-06	725.7	728.7	0.063	630	0.01	0.6	74	42	6	31	0.01	6	1.6	2.0	104	0.01
KL44-06	728.7	730.9	0.062	620	0.01	0.6	80	38	4	30	0.01	7	1.5	3.0	106	0.01
KL44-06	730.9	733.9	0.124	1240	0.01	0.7	144	57	32	67	1	22	2.2	3.5	110	0.01
KL44-06	733.9	737	0.203	2030	0.11	0.7	291	169	25	48	1	13	9.2	4.3	91	0.12
KL44-06	737	740.1	0.236	2360	0.05	1.2	168	41	18	156	1	18	13.3	3.8	135	0.01
KL44-06	740.1	743.2	0.23	2300	0.08	0.1	122	33	2	39	0.01	12	0.7	3.9	104	0.01
KL44-06	743.2	746.2	0.145	1450	0.01	0.5	42	28	2	36	0.01	8	0.3	2.8	135	0.01
KL44-06	746.2	749.3	0.191	1910	0.05	1.3	82	165	22	179	1	9	0.3	2.0	147	0.01
KL44-06	749.3	751.9	0.23	2300	0.1	1.3	325	161	16	43	1	10	0.6	4.3	101	0.01
KL44-06	751.9	754.8	0.154	1540	0.03	0.1	57	16	3	61	3	10	0.01	3.8	113	0.01
KL44-06	754.8	757.9	0.32	3200	0.06	1.1	98	47	40	70	4	14	3.2	8.5	98	0.01
KL44-06	757.9	761	0.284	2840	0.12	0.8	230	158	14	94	1	15	1.4	15.0	95	0.11
KL44-06	761	764.1	0.145	1450	0.03	0.1	274	121	34	96	1	13	1.4	9.3	148	0.15
KL44-06	764.1	767.2	0.156	1560	0.02	1	177	118	25	83	1	12	2.4	7.0	254	0.01
KL44-06	767.2	770.3	0.098	980	0.01	0.6	212	97	44	73	1	6	2.8	5.3	215	0.1
KL44-06	770.3	773.4	0.165	1650	0.02	1.2	1050	630	170	27	0.01	10	11.9	6.9	147	0.27
KL44-06	773.4	776.5	0.147	1470	0.01	0.1	368	159	76	62	1	9	1.8	4.8	186	0.01
KL44-06	776.5	779.6	0.166	1660	0.02	0.8	224	182	34	206	1	14	2	5.7	180	0.12
KL44-06	779.6	782.7	0.256	2560	0.14	0.6	68	48	11	43	0.01	8	0.3	4.5	122	0.01
KL44-06	782.7	785.7	0.165	1650	0.11	0.1	50	26	1	41	0.01	12	0.01	4.3	112	0.01
KL44-06	785.7	788.7	0.118	1180	0.38	0.5	530	38	43	27	1	8	3.1	2.8	110	0.1
KL44-06	788.7	791.7	0.102	1020	0.09	0.1	182	64	3	128	1	10	0.7	4.5	103	0.01
KL44-06	791.7	794.7	0.103	1030	0.12	0.1	33	13	12	142	0.01	6	2.5	5.0	93	0.01
KL44-06	794.7	797.7	0.22	2200	0.02	0.6	377	126	34	261	1	18	1.9	9.3	122	0.1
KL44-06	797.7	800.7	0.22	2200	0.05	0.1	93	45	2	256	0.01	11	0.2	7.0	125	0.01
KL44-06	800.7	803.7	0.197	1970	0.1	0.6	130	58	18	1200	0.01	13	0.2	13.9	99	0.01
KL44-06	803.7	806.7	0.117	1170	0.04	0.1	209	87	140	299	1	9	0.8	4.5	108	0.1
KL44-06	806.7	809.7	0.135	1350	0.03	1.1	342	171	120	120	2	10	12.3	6.3	96	0.01
KL44-06	809.7	812.7	0.199	1990	0.08	2.5	260	320	52	789	2	14	36	10.0	103	0.01
KL44-06	812.7	815.7	0.09	900	0.03	0.1	176	137	15	62	0.01	12	8.6	4.5	127	0.01
KL44-06	815.7	818.7	0.1	1000	0.02	1.4	480	430	32	59	2	11	2.7	7.5	106	0.01
KL44-06	818.7	821.7	0.07	700	0.02	1.6	356	207	40	55	1	12	1.8	9.0	170	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL44-06	821.7	824.7	0.26	2600	0.52	85	470	1200	80	38	14	9	240	14.7	148	0.21
KL44-06	824.7	827.7	0.56	5600	0.66	118	460	9300	90	51	58	12	51	15.5	156	0.34
KL44-06	827.7	830.7	0.135	1350	0.03	1.9	372	277	30	232	2	20	2.3	12.8	91	0.01
KL44-06	830.7	833.7	0.073	730	0.03	0.7	234	163	11	68	2	12	1.6	8.4	110	0.01
KL44-06	833.7	836.7	0.152	1520	0.04	1.5	440	389	15	120	3	13	1.7	6.5	113	0.01
KL44-06	836.7	839.7	0.156	1560	0.05	1	370	239	18	84	2	10	2	6.3	156	0.01
KL44-06	839.7	842.5	0.113	1130	0.04	1.1	244	156	41	980	1	9	20.9	3.8	96	0.01
KL44-07	0	2.4	0.0025	25	0.01	0.1	48	34	7	4	0.01	1	0.5	1.0	30	0.01
KL44-07	2.4	5.4	0.163	1630	0.15	0.8	162	76	32	23	2	1	1.5	2.0	35	0.16
KL44-07	5.4	7.4	0.0031	31	0.03	0.1	44	18	11	4	0.01	1	1.1	0.7	33	0.11
KL44-07	7.4	10.6	0.0029	29	0.05	1.5	93	66	21	2	0.01	1	2.5	2.4	25	0.01
KL44-07	10.6	14.4	0.087	870	0.08	1	181	66	32	8	0.01	1	1.9	2.3	23	0.01
KL44-07	14.4	17	0.002	20	0.01	0.1	43	23	16	4	0.01	1	0.6	1.7	18	0.01
KL44-07	17	20.1	0.0019	19	0.01	0.1	60	18	16	3	0.01	1	0.6	1.5	22	0.01
KL44-07	20.1	23.2	0.0041	41	0.02	1.2	760	361	37	7	0.01	1	2.1	2.1	30	0.01
KL44-07	23.2	26.3	0.0029	29	0.01	0.1	97	32	8	7	0.01	1	0.4	1.0	24	0.01
KL44-07	26.3	29.4	0.006	60	0.01	0.1	54	17	4	3	0.01	1	0.2	0.8	19	0.01
KL44-07	29.4	32.4	0.0135	135	0.32	8.1	6200	3700	110	12	0.01	1	27.3	65.0	27	0.33
KL44-07	32.4	35.4	0.0021	21	0.01	0.1	152	54	8	2	0.01	1	1.1	1.7	21	0.01
KL44-07	35.4	38.4	0.0024	24	0.01	0.1	301	234	9	3	0.01	1	0.9	1.3	21	0.01
KL44-07	38.4	41.4	0.002	20	0.23	1.4	368	81	13	3	0.01	1	3	2.1	20	0.27
KL44-07	41.4	44.4	0.0013	13	0.01	0.1	40	24	6	3	0.01	1	0.5	1.4	15	0.01
KL44-07	44.4	46.9	0.0024	24	0.01	0.1	26	14	10	2	0.01	1	0.9	2.4	19	0.01
KL44-07	46.9	50.4	0.0025	25	0.02	0.1	33	13	5	2	0.01	1	0.7	1.4	21	0.01
KL44-07	50.4	53.2	0.002	20	0.04	0.1	37	14	3	2	0.01	1	0.4	1.7	18	0.01
KL44-07	53.2	56.3	0.0031	31	0.03	0.8	28	16	7	7	0.01	1	1	1.8	20	0.12
KL44-07	56.3	59.4	0.182	1820	0.18	1.6	140	84	34	49	1	6	2.5	5.0	45	0.21
KL44-07	59.4	62.4	0.0113	113	0.08	0.6	43	28	19	5	0.01	1	1.3	2.1	23	0.01
KL44-07	62.4	65.4	0.0029	29	0.03	0.1	39	43	13	3	0.01	1	0.5	1.9	25	0.01
KL44-07	65.4	68.1	0.0102	102	0.04	1.2	100	180	34	3	5	1	1.1	7.0	38	0.01
KL44-07	68.1	71.1	0.0106	106	0.02	0.1	105	99	22	3	0.01	1	0.6	2.5	22	0.01
KL44-07	71.1	74.2	0.0032	32	0.01	0.1	56	81	20	2	0.01	1	0.6	1.8	24	0.01
KL44-07	74.2	77.4	0.0046	46	0.02	2.1	1710	250	24	33	64	3	1.1	15.3	36	0.01
KL44-07	77.4	80.4	0.0106	106	0.09	0.1	165	40	100	76	14	2	3.2	3.2	70	0.01
KL44-07	80.4	82.4	0.0133	133	0.06	0.1	205	47	53	114	4	1	1.5	3.1	73	0.01
KL44-07	82.4	85.1	0.22	2200	0.21	38	10100	1830	490	560	280	9	13.8	36.0	57	2.38
KL44-07	85.1	87.7	0.209	2090	0.23	14.2	15400	620	420	9	240	13	13.6	61.5	37	2.64
KL44-07	87.7	89.4	0.0226	226	0.22	3.2	5600	1560	120	420	8	1	12	20.5	24	0.44
KL44-07	89.4	92.4	0.0165	165	0.2	0.9	380	254	82	116	3	1	6.6	4.5	41	0.25
KL44-07	92.4	95.2	0.0173	173	0.23	0.7	870	211	59	20	11	1	5.5	2.6	35	0.33
KL44-07	95.2	98.8	0.0154	154	0.13	0.7	460	142	62	12	6	1	5	3.4	29	0.01
KL44-07	98.8	101.1	0.013	130	0.28	0.9	740	276	77	24	6	1	5.8	8.3	25	0.12
KL44-07	101.1	104.4	0.0145	145	0.11	1.2	600	139	48	53	10	1	3.1	4.7	23	0.12
KL44-07	104.4	107	0.0174	174	0.25	0.9	760	185	250	57	15	1	12.2	1.8	31	0.28
KL44-07	107	109.7	0.0076	76	0.05	0.1	152	50	270	49	1	1	5.9	1.3	30	0.01
KL44-07	109.7	113.3	0.0106	106	0.08	0.9	160	118	83	214	52	3	7.6	11.3	19	0.01
KL44-07	113.3	116.5	0.039	390	0.11	1.4	520	290	120	160	15	1	12	8.5	18	0.01
KL44-07	116.5	119.6	0.36	3600	0.16	3.2	3560	358	510	217	10	9	19	12.3	30	0.14
KL44-07	119.6	122.5	0.027	270	0.12	1.5	1870	560	73	174	6	1	14.9	8.0	36	0.14
KL44-07	122.5	125.8	0.0202	202	0.05	1.8	820	376	50	24	18	1	4.8	5.4	17	0.01
KL44-07	125.8	128.7	0.0065	65	0.04	1.2	480	225	15	18	4	1	1.5	5.1	19	0.01
KL44-07	128.7	131.3	0.0037	37	0.05	0.8	420	126	15	24	6	1	1.4	3.6	16	0.01
KL44-07	131.3	133.8	0.0071	71	0.04	1.2	460	158	26	42	7	1	2.2	4.9	20	0.01
KL44-07	133.8	137	0.019	190	0.07	1.4	520	266	30	24	4	1	3.1	3.3	21	0.01
KL44-07	137	140.1	0.0095	95	0.07	2.4	1780	890	35	22	11	1	5.2	9.3	23	0.01
KL44-07	140.1	142.7	0.0031	31	0.04	0.6	341	171	13	27	2	1	1.3	1.5	22	0.01
KL44-07	142.7	145.6	0.0024	24	0.03	0.5	232	83	11	18	2	1	0.8	1.2	19	0.01
KL44-07	145.6	148.9	0.002	20	0.03	0.5	248	66	6	78	2	1	0.6	0.8	21	0.01
KL44-07	148.9	151.6	0.0058	58	0.19	2.1	610	243	250	227	5	1	4	4.5	27	0.01
KL44-07	151.6	155.4	0.0199	199	0.09	0.8	630	135	58	41	6	1	1.4	2.5	26	0.14
KL44-07	155.4	158.6	0.0072	72	0.06	1.5	1050	409	24	25	6	1	1.2	4.5	19	0.01
KL44-07	158.6	161.7	0.0207	207	0.08	2.2	1060	480	64	27	6	1	3.8	5.8	12	0.1
KL44-07	161.7	164.3	0.0109	109	0.03	0.9	460	97	26	33	10	1	2.3	1.8	11	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL44-07	164.3	167.4	0.0125		125	0.06	1.1	650	261	28	27	4	1	1.4	3.8	10	0.01
KL44-07	167.4	170.2	0.0115		115	0.04	1.3	1990	690	28	22	1	3	2.1	3.2	11	0.01
KL44-07	170.2	173.3	0.0325		325	0.04	1.2	530	120	120	20	1	1	4	2.7	13	0.01
KL44-07	173.3	176.8	0.0147		147	0.04	1	910	500	12	22	2	1	1.2	3.1	15	0.01
KL44-07	176.8	179.5	0.0205		205	0.05	1.6	1220	510	24	32	3	1	1	4.3	14	0.01
KL44-07	179.5	182.6	0.0296		296	0.03	2	1110	600	54	25	5	1	2	4.1	11	0.01
KL44-07	182.6	185	0.0311		311	0.04	2.4	1820	1410	59	44	4	1	2.5	7.2	12	0.01
KL44-07	185	187.9	0.042		420	0.05	1.5	1190	420	77	26	2	1	2.3	2.6	12	0.01
KL44-07	187.9	190.5	0.184		1840	0.13	5.3	2400	960	150	63	10	2	2.4	6.2	18	0.01
KL44-07	190.5	194.3	1.31		13100	1.15	24.3	4000	780	850	337	40	7	6.8	17.0	48	0.24
KL44-07	194.3	197.4	0.135		1350	0.36	13.4	8000	9200	120	167	32	2	8.3	17.5	32	0.22
KL44-07	197.4	200.4	0.062		620	0.4	7.5	9300	7500	180	50	7	5	11.3	18.0	30	0.27
KL44-07	200.4	203.2	0.0228		228	0.21	2.8	3200	700	89	17	6	2	2.2	5.8	21	0.15
KL44-07	203.2	205.4	0.061		610	0.29	2.1	3300	610	140	5	1	3	3.2	4.4	26	0.11
KL44-07	205.4	207.4	0.0291		291	0.29	1.5	2900	399	110	4	2	1	2.1	3.1	18	0.14
KL44-07	207.4	209.6	1.11		11100	1.57	18.9	5000	261	370	56	48	27	3.8	21.5	104	0.22
KL44-07	209.6	211.8	1.61		16100	3.76	23.2	8400	223	780	84	80	35	9.8	18.4	78	0.7
KL44-07	211.8	214.8	0.4		4000	1.85	7.5	7200	269	550	58	32	29	9.5	16.3	47	0.34
KL44-07	214.8	218.4	0.75		7500	4.14	12.5	71000	231	1060	36	22	91	14.3	36.0	103	1.07
KL44-07	218.4	221.2	1.1		11000	2.82	18.8	3250	170	530	295	28	55	8.5	22.7	66	0.36
KL44-07	221.2	224.3	0.71		7100	1.72	8.8	3300	235	320	42	10	26	10.5	14.3	58	0.01
KL44-07	224.3	227	0.675		6750	1.36	12.1	2300	73	80	73	19	17	2.6	32.4	50	0.01
KL44-07	227	230.1	0.32		3200	0.95	4.7	163	61	100	61	36	14	4.5	10.8	30	0.14
KL44-07	230.1	233.1	1.63		16300	2.42	12.8	338	65	150	137	22	25	7.4	16.5	58	0.01
KL44-07	233.1	236.4	2.2		22000	1.78	12.4	1300	890	530	303	18	29	18.7	17.2	167	0.24
KL44-07	236.4	239.4	1.48		14800	1.62	7.4	1110	440	160	180	9	21	4.8	21.5	72	0.01
KL44-07	239.4	242.4	0.74		7400	1.22	7.7	630	2300	150	560	7	35	8.5	19.0	120	0.01
KL44-07	242.4	245.4	0.6		6000	1.36	11.6	197	1130	170	321	14	60	7.8	25.3	80	0.01
KL44-07	245.4	248.4	0.76		7600	1.3	4	190	396	140	150	54	27	5.3	18.3	46	0.01
KL44-07	248.4	251.4	0.59		5900	1	4	147	216	180	45	4	25	5.8	7.5	141	0.01
KL44-07	251.4	254.4	1.25		12500	1.11	4.1	302	202	37	470	5	46	3	27.0	104	0.01
KL44-07	254.4	257.4	1.45		14500	2.63	3.4	241	129	49	168	6	27	3.8	19.5	78	0.01
KL44-07	257.4	259.9	2.29		22900	1.86	3.7	245	143	45	118	6	32	4	23.0	58	0.01
KL44-07	259.9	262.8	1.21		12100	0.7	3.3	310	174	75	45	7	40	5.3	8.0	62	0.01
KL44-07	262.8	266.4	0.59		5900	0.55	3.9	5260	3970	110	129	4	26	7.3	8.3	80	0.1
KL44-07	266.4	269.4	1.77		17700	0.89	3	2400	1100	110	28	3	27	7	17.0	80	0.01
KL44-07	269.4	272.2	0.59		5900	0.39	1.5	88	63	43	33	2	23	4	8.0	104	0.01
KL44-07	272.2	275.3	0.48		4800	0.51	2.3	660	960	110	14	1	22	6.5	7.3	105	0.01
KL44-07	275.3	278.3	0.83		8300	0.55	2.7	820	480	140	318	2	46	5.8	18.8	98	0.01
KL44-07	278.3	281.4	1.67		16700	0.94	4.3	203	209	310	76	1	36	11.5	8.8	78	0.01
KL44-07	281.4	284.2	0.64		6400	0.51	2.6	102	141	90	107	1	20	3.5	6.0	56	0.01
KL44-07	284.2	287.4	0.65		6500	0.64	2.9	157	99	55	1940	1	63	3	16.8	68	0.01
KL44-07	287.4	290.4	0.8		8000	0.68	2.3	210	275	73	225	1	35	3.5	15.0	74	0.01
KL44-07	290.4	293.4	1.3		13000	0.87	3.4	201	138	91	68	1	36	3.8	15.0	55	0.01
KL44-07	293.4	296.3	0.29		2900	0.28	1	223	224	41	403	5	20	2	18.8	49	0.01
KL44-07	296.3	299.4	0.3		3000	0.33	1.6	106	124	51	620	18	20	2.4	17.8	64	0.01
KL44-07	299.4	302.4	0.78		7800	0.52	3.7	121	338	45	3690	18	24	8.8	26.0	71	0.01
KL44-07	302.4	305.4	0.53		5300	0.6	2.4	530	1620	38	1280	9	23	7	24.3	55	0.01
KL44-07	305.4	308.4	0.22		2200	0.4	1.2	171	115	58	1470	4	18	2.5	19.0	43	0.01
KL44-07	308.4	311.4	0.25		2500	0.2	0.5	135	61	27	950	3	38	1.5	23.5	53	0.01
KL44-07	311.4	314.4	0.32		3200	0.75	0.7	101	58	55	1010	5	11	2	24.3	67	0.01
KL44-07	314.4	317.4	0.4		4000	0.41	0.7	163	90	36	760	3	9	1.3	20.8	83	0.01
KL44-07	317.4	320.4	0.42		4200	0.36	1	213	58	46	590	3	10	1.4	19.2	43	0.01
KL44-07	320.4	323.4	1.14		11400	0.71	3.4	500	175	99	680	5	13	3.5	9.4	60	0.01
KL44-07	323.4	326.4	0.99		9900	0.41	2.5	313	198	75	570	5	15	2.5	13.0	50	0.01
KL44-07	326.4	329.7	0.54		5400	0.43	2.4	3420	302	100	112	7	16	3.5	13.8	56	0.01
KL44-07	329.7	332.4	3.45		34500	2.12	10.5	830	307	280	4	26	37	7.4	20.0	104	0.01
KL44-07	332.4	335.4	2.15		21500	1.52	8.4	188	125	290	3	20	34	4.6	18.0	107	0.01
KL44-07	335.4	338.4	1.58		15800	3.22	4	217	131	200	6	12	27	8.2	17.0	40	0.01
KL44-07	338.4	341.4	1.67		16700	2.93	11.3	4400	440	470	7	37	111	9.9	18.8	53	0.01
KL44-07	341.4	343.4	1.04		10400	1.8	6.7	223	203	200	3	22	20	8.1	3.5	72	0.01
KL44-07	343.4	345.4	0.187		1870	1.14	1.6	1160	530	54	3	26	23	3.6	1.5	70	0.01
KL44-07	345.4	347.5	0.64		6400	2.1	15.6	65500	3500	560	2	54	2	14.2	10.2	78	0.12

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL44-07	347.5	350.4	0.0303	303	0.45	9.1	16000	5200	190	4	6	2	8.5	2.8	21	0.01
KL44-07	350.4	353.4	0.112	1120	1.17	16.7	57500	9500	450	6	18	1	9	8.5	27	0.12
KL44-07	353.4	356.4	0.37	3700	0.65	1	80	19	2	10	1	9	0.01	3.4	68	0.01
KL44-07	356.4	359.4	0.065	650	0.24	6.3	13400	5300	260	35	1	1	5.8	2.6	23	0.01
KL44-07	359.4	362.4	0.062	620	0.48	9.5	19000	6500	340	4	0.01	1	10.8	1.5	27	0.01
KL44-07	362.4	364.5	0.072	720	0.71	35	38100	25000	330	5	1	2	36	2.1	21	0.01
KL44-07	364.5	368.4	0.173	1730	0.86	4.3	1630	863	68	17	5	6	2.4	2.2	22	0.01
KL44-07	368.4	371.4	0.0174	174	0.46	0.9	920	580	46	19	1	2	1.5	1.0	23	0.01
KL44-07	371.4	374.4	0.065	650	0.39	14.7	7000	3700	95	45	38	4	3	5.4	25	0.01
KL44-07	374.4	377.4	0.043	430	0.53	7.1	10000	5100	410	76	14	4	8.8	3.9	28	0.01
KL44-07	377.4	380.4	0.027	270	0.23	6.6	10400	9000	70	263	4	3	7.6	1.5	20	0.01
KL44-07	380.4	383.4	0.055	550	0.16	0.8	520	244	29	167	1	3	0.9	1.0	18	0.01
KL44-07	383.4	386.4	0.0171	171	0.11	0.5	640	305	43	73	4	1	1.3	1.4	17	0.01
KL44-07	386.4	389.4	0.0259	259	0.04	1.1	690	296	27	258	3	3	0.8	0.8	20	0.01
KL44-07	389.4	392.4	0.0253	253	0.04	4.5	2100	5300	26	24	0.01	3	5.8	0.8	21	0.01
KL44-07	392.4	395.4	0.0203	203	0.1	1.5	4900	2100	70	11	1	3	4.4	1.4	24	0.01
KL44-07	395.4	398.4	0.0196	196	0.05	0.1	470	56	32	14	2	3	0.7	0.0	28	0.01
KL44-07	398.4	401.4	0.012	120	0.08	0.1	690	197	45	54	3	2	1.8	0.8	19	0.01
KL44-07	401.4	404.4	0.015	150	0.11	0.1	376	141	53	6	0.01	2	2.6	1.5	18	0.01
KL44-07	404.4	407.4	0.004	40	0.07	0.1	410	168	38	10	2	1	2.8	1.1	31	0.01
KL44-07	407.4	410.4	0.0063	63	0.07	0.1	1050	540	36	7	4	1	2.6	1.5	25	0.01
KL44-07	410.4	413.4	0.0093	93	0.02	0.1	620	287	44	12	0.01	1	1.2	1.7	21	0.01
KL44-07	413.4	416.4	0.103	1030	0.13	1.3	1470	1470	100	14	2	10	4.4	7.7	29	0.01
KL44-07	416.4	419.4														
KL44-07	419.4	422.4	0.0151	151	0.23	0.5	362	378	160	19	5	1	3.3	2.6	40	0.01
KL44-07	422.4	425.4	0.0199	199	0.2	1.2	8000	3100	160	22	2	3	4.8	2.5	24	0.01
KL44-07	425.4	428.4	0.135	1350	0.35	4.7	6600	3400	190	36	26	10	3.9	21.0	33	0.01
KL44-07	428.4	431.4	0.72	7200	0.88	13.5	2200	244	550	173	20	170	15.3	65.0	46	0.01
KL44-07	431.4	434.4	0.062	620	0.09	0.1	410	70	40	20	13	4	2.4	2.7	21	0.01
KL44-07	434.4	437.4	0.0042	42	0.02	0.1	201	31	54	6	0.01	3	2.3	1.3	23	0.01
KL44-07	437.4	440.4	0.0059	59	0.02	0.1	98	36	23	4	0.01	3	1.1	1.3	15	0.01
KL44-07	440.4	443	0.0087	87	0.14	0.1	285	119	47	6	0.01	1	2.2	1.6	20	0.01
KL44-07	443	444.4	0.527	5270	1.24	1.6	185	87	130	44	6	81	5.3	17.5	33	0.01
KL44-07	444.4	445.9	1.25	12500	1.22	1.9	227	122	23	79	2	50	3.3	34.5	38	0.01
KL44-07	445.9	448.9	1.48	14800	2.24	2.6	378	124	19	86	2	64	3.7	22.5	41	0.01
KL44-07	448.9	452	0.64	6400	1.26	1	365	214	200	58	2	12	3.6	9.3	63	0.01
KL44-07	452	455.1	0.169	1690	0.42	1.5	450	206	110	413	7	11	2.2	2.5	54	0.01
KL44-07	455.1	458.2	0.259	2590	0.51	3.2	650	730	150	156	24	14	4.2	7.0	110	0.01
KL44-07	458.2	461.2	0.419	4190	0.2	1.8	145	123	85	610	9	9	1.1	5.4	65	0.01
KL44-07	461.2	464.2	0.321	3210	0.13	1	112	55	54	470	6	4	0.7	5.2	83	0.01
KL44-07	464.2	465.9	0.315	3150	0.09	0.9	59	25	72	325	8	1	0.6	4.0	70	0.01
KL44-07	465.9	467.4	0.311	3110	0.09	1.6	83	73	88	1900	10	6	0.8	5.8	130	0.01
KL44-07	467.4	469.9	0.76	7600	0.49	8.7	4000	3900	300	1036	8	10	7.3	5.6	95	0.01
KL44-07	469.9	472.5	0.78	7800	0.61	8.8	5500	3400	340	884	5	8	7.6	10.0	91	0.01
KL44-07	472.5	475.6	0.358	3580	0.21	1.7	430	263	84	870	0.01	4	1.2	4.2	92	0.01
KL44-07	475.6	478.7	3.03	30300	7.59	8	178	63	270	615	112	30	1.7	18.0	61	0.01
KL44-07	478.7	481.8	1.52	15200	3.92	3.8	135	15	400	24	4	60	2.4	15.5	48	0.01
KL44-07	481.8	483.7	1.36	13600	1.85	4.4	640	28	590	46	7	50	4.6	20.5	49	0.01
KL44-07	483.7	485.8	1.64	16400	3.22	4.9	590	85	1450	11	4	66	22	18.0	88	0.01
KL44-07	485.8	488.4	0.184	1840	0.53	0.9	153	60	200	10	2	9	6.8	4.8	26	0.01
KL44-07	488.4	491.4	0.0038	38	0.03	0.1	66	15	18	1	0.01	1	0.4	1.8	18	0.01
KL44-07	491.4	494.4	0.0041	41	0.02	0.1	29	13	9	1	1	2	0.4	2.6	18	0.01
KL44-07	494.4	497.4	0.0042	42	0.03	0.1	33	12	11	4	1	1	0.5	1.3	15	0.01
KL44-07	497.4	500.4	0.0029	29	0.01	0.1	30	13	8	1	1	1	0.4	1.3	15	0.01
KL44-07	500.4	502.9	0.0058	58	0.06	0.1	89	24	34	4	2	1	0.9	2.3	21	0.01
KL44-07	502.9	504.9	0.0024	24	0.01	0.1	70	18	8	1	1	1	0.4	1.1	13	0.01
KL44-07	504.9	508	0.0035	35	0.01	0.1	38	13	9	8	0.01	1	0.3	0.9	13	0.01
KL44-07	508	510.5	0.003	30	0.02	0.1	98	24	9	2	0.01	1	0.4	1.1	13	0.01
KL44-07	510.5	512.6	0.0021	21	0.01	0.1	39	12	7	1	0.01	1	0.3	1.0	14	0.01
KL44-07	512.6	515.4	0.0117	117	0.02	0.1	64	21	20	4	0.01	1	0.8	1.7	18	0.01
KL44-07	515.4	518.4	0.0018	18	0.01	0.1	49	22	5	1	0.01	1	0.3	1.6	14	0.01
KL44-07	518.4	521.4	0.0036	36	0.01	0.1	47	15	10	2	0.01	1	0.6	1.3	21	0.01
KL44-07	521.4	524.4	0.0015	15	0.01	0.1	32	14	6	2	0.01	1	0.3	0.8	18	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL44-07	524.4	527.4	0.0028		28	0.01	0.1	26	10	7	3	0.01	1	0.2	0.8	18	0.01
KL44-07	527.4	530.4	0.0038		38	0.01	0.1	25	10	10	4	0.01	1	0.7	1.7	18	0.01
KL44-07	530.4	532.6	0.0029		29	0.01	0.1	25	9	10	3	0.01	1	0.2	1.1	17	0.01
KL44-07	532.6	535.7	0.0098		98	0.01	0.1	56	21	10	4	0.01	1	0.6	2.3	24	0.01
KL44-07	535.7	537.5	0.0069		69	0.04	0.1	49	18	18	10	0.01	3	1	1.3	21	0.01
KL44-07	537.5	539.4	0.0014		14	0.04	0.1	34	9	19	7	0.01	1	1.3	1.3	26	0.01
KL44-07	539.4	542.4	0.005		50	0.05	0.1	155	27	29	4	0.01	1	1.2	1.7	11	0.01
KL44-07	542.4	545.4	0.0014		14	0.02	0.1	183	23	12	4	0.01	1	0.7	0.7	26	0.01
KL44-07	545.4	547.5	0.0033		33	0.05	0.1	201	36	29	4	0.01	1	2.3	1.2	17	0.01
KL44-07	547.5	549.4	0.0029		29	0.05	0.1	470	124	22	3	0.01	1	1.1	1.4	18	0.01
KL44-07	549.4	551.4	0.0084		84	0.04	1.2	930	412	10	6	0.01	1	1.4	14.0	18	0.01
KL44-07	551.4	553.8	0.0016		16	0.03	0.1	490	40	20	1	0.01	1	0.4	1.1	16	0.01
KL44-07	553.8	555.5	0.0093		93	0.01	0.1	85	21	10	1	0.01	1	0.6	0.7	20	0.01
KL44-07	555.5	557.4	0.0038		38	0.04	0.1	120	27	24	5	0.01	1	1	2.0	18	0.01
KL44-07	557.4	560.4	0.0112		112	0.02	0.1	490	234	15	6	0.01	1	0.5	3.6	15	0.01
KL44-07	560.4	563.4	0.0021		21	0.04	0.1	60	23	18	3	0.01	1	0.5	1.6	25	0.01
KL44-07	563.4	566.4	0.0017		17	0.1	0.1	57	15	18	3	0.01	1	0.7	0.7	25	0.01
KL44-07	566.4	569.4	0.0323		323	0.06	0.1	131	48	6	3	0.01	1	0.4	4.4	42	0.01
KL44-07	569.4	572.4	0.0022		22	0.01	0.1	29	11	3	4	0.01	1	0.2	0.5	18	0.01
KL44-07	572.4	575.4	0.0029		29	0.02	0.1	32	9	9	2	0.01	1	0.4	1.0	20	0.01
KL44-07	575.4	578.4	0.0036		36	0.14	0.6	90	27	55	6	0.01	1	3	3.3	28	0.01
KL44-07	578.4	581.4	0.0035		35	0.19	0.1	46	15	16	3	0.01	1	2	1.7	26	0.01
KL44-07	581.4	584.4	0.0019		19	0.02	0.1	28	11	6	2	0.01	1	0.4	1.0	17	0.01
KL44-07	584.4	587.4	0.0014		14	0.03	0.1	82	10	6	3	0.01	1	0.5	2.1	15	0.01
KL44-07	587.4	590.4	0.0009		9	0.01	0.1	68	16	8	4	0.01	1	0.3	1.2	17	0.01
KL44-07	590.4	593.4	0.001		10	0.01	0.1	32	16	8	6	0.01	1	0.4	1.6	21	0.01
KL44-07	593.4	596.4	0.0017		17	0.01	0.1	34	10	8	4	0.01	1	0.2	1.2	17	0.01
KL44-07	596.4	599.4	0.0008		8	0.01	0.1	20	11	5	3	0.01	1	0.2	0.6	15	0.01
KL44-07	599.4	601.7	0.0007		7	0.01	0.1	23	14	6	5	0.01	1	0.3	0.9	17	0.01
KL44-07	601.7	604.8	0.001		10	0.01	0.1	20	14	9	5	0.01	1	0.3	0.7	23	0.01
KL44-07	604.8	607.8	0.0032		32	0.01	0.1	19	16	9	5	0.01	1	0.3	0.6	18	0.01
KL44-07	607.8	610.9	0.0017		17	0.01	0.1	32	17	15	5	0.01	1	0.3	0.7	19	0.01
KL44-07	610.9	614	0.0008		8	0.01	0.1	17	9	6	3	0.01	1	0.3	1.2	17	0.01
KL44-07	614	617.1	0.0016		16	0.04	0.1	61	28	21	7	0.01	1	0.8	2.3	40	0.01
KL44-07	617.1	620.2	0.0035		35	0.03	0.1	16	14	9	4	0.01	1	0.5	1.3	18	0.01
KL44-07	620.2	623.3	0.0032		32	0.01	0.1	108	36	9	8	0.01	1	0.7	1.9	17	0.01
KL44-07	623.3	626.4	0.0009		9	0.01	0.1	37	17	7	3	0.01	1	0.4	0.8	16	0.01
KL44-07	626.4	629.4	0.0009		9	0.01	0.1	42	18	6	4	0.01	1	0.2	0.9	18	0.01
KL44-07	629.4	632.4	0.0017		17	0.02	0.1	49	16	7	3	0.01	1	0.2	1.0	17	0.01
KL44-07	632.4	635.4	0.001		10	0.02	0.1	49	17	6	5	0.01	1	0.01	1.2	16	0.01
KL44-07	635.4	638.4	0.0008		8	0.01	0.1	30	16	5	3	0.01	1	0.2	0.0	16	0.01
KL44-08	0	2	0.0065		65	0.01	0.7	178	253	10	2	0.01	1	2	0.9	18	0.01
KL44-08	2	4.1	0.0075		75	0.05	0.6	114	54	13	1	0.01	1	1.3	0.7	19	0.01
KL44-08	4.1	5.9	0.0112		112	0.07	0.7	193	81	17	4	0.01	1	0.9	0.7	22	0.01
KL44-08	5.9	8.4	0.0042		42	0.01	0.1	56	39	3	1	0.01	1	0.3	0.0	18	0.01
KL44-08	8.4	10.4	0.0115		115	0.01	0.1	73	61	8	1	0.01	1	0.9	1.3	21	0.01
KL44-08	10.4	13.4	0.0058		58	0.02	1	185	101	17	22	0.01	1	1.7	2.6	18	0.01
KL44-08	13.4	16.5	0.0037		37	0.02	0.8	69	50	14	2	0.01	1	1	1.8	18	0.01
KL44-08	16.5	19.6	0.004		40	0.02	0.5	63	42	20	6	0.01	1	1.5	2.0	17	0.01
KL44-08	19.6	22.7	0.0019		19	0.03	0.1	213	42	16	2	0.01	1	1.9	1.8	22	0.01
KL44-08	22.7	25.8	0.0038		38	0.03	1	580	76	29	20	1	1	3.2	3.1	22	0.01
KL44-08	25.8	28.9	0.0071		71	0.08	1.9	1520	107	32	3	0.01	1	7.8	4.1	24	0.01
KL44-08	28.9	31.8	0.0094		94	0.13	9.3	2570	748	110	34	5	1	7.7	10.1	16	0.5
KL44-08	31.8	33.6	0.0194		194	0.38	11.6	3560	3500	120	11	1	1	16.8	6.7	18	0.46
KL44-08	33.6	35.1	0.0167		167	0.11	1.3	1580	206	31	52	4	3	2.3	5.6	17	0.12
KL44-08	35.1	38.1	0.0112		112	0.01	0.1	147	61	10	3	0.01	1	1.5	2.0	19	0.01
KL44-08	38.1	41.1	0.004		40	0.02	0.1	76	51	7	6	0.01	1	0.7	3.2	21	0.01
KL44-08	41.1	43.1	0.0028		28	0.05	0.5	107	63	13	1	0.01	1	1.8	2.0	19	0.01
KL44-08	43.1	46.2	0.005		50	0.04	1.6	361	199	16	2	2	1	2.8	2.8	20	0.1
KL44-08	46.2	49.3	0.0046		46	0.04	1	510	160	24	1	0.01	1	2.5	1.9	26	0.01
KL44-08	49.3	52.4	0.0015		15	0.02	0.1	52	41	14	2	0.01	1	0.8	2.1	21	0.01
KL44-08	52.4	55.5	0.0018		18	0.01	0.1	43	24	6	2	0.01	1	0.3	1.1	23	0.01
KL44-08	55.5	58.6	0.0021		21	0.01	0.1	99	49	13	3	0.01	1	0.8	1.3	21	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL44-08	58.6	61.2	0.0124		124	0.01	0.1	44	28	16	11	0.01	1	1.6	1.3	20	0.01
KL44-08	61.2	64.2	0.0022		22	0.02	0.1	43	23	21	3	0.01	1	1.1	1.7	20	0.01
KL44-08	64.2	67.3	0.003		30	0.02	0.1	47	54	22	6	0.01	2	0.9	2.5	26	0.01
KL44-08	67.3	70.4	0.0064		64	0.03	1.1	233	231	45	7	3	1	1.8	10.5	42	0.01
KL44-08	70.4	73.4	0.0034		34	0.11	0.1	116	83	25	4	0.01	3	2	3.7	21	0.01
KL44-08	73.4	76.4	0.0049		49	0.01	0.1	67	79	9	2	0.01	1	1.3	2.1	18	0.01
KL44-08	76.4	77.8	0.0304		304	0.04	0.1	242	82	24	74	4	1	2	4.3	23	0.01
KL44-08	77.8	80.1	0.0034		34	0.03	0.1	246	105	25	1	2	1	3.6	3.9	22	0.01
KL44-08	80.1	83.1	0.0134		134	0.06	0.1	264	210	31	4	1	1	2.4	4.9	35	0.01
KL44-08	83.1	86.1	0.0118		118	0.21	1.3	660	410	140	20	6	3	6.3	8.9	45	0.01
KL44-08	86.1	88.2	0.067		670	0.71	3.1	2260	870	82	108	25	6	5.6	21.5	81	0.01
KL44-08	88.2	89.6	0.0188		188	0.34	2	2780	408	120	24	4	7	10.5	4.5	87	0.18
KL44-08	89.6	92.1	0.094		940	1.36	22.6	14400	5700	370	25	66	4	113	69.2	40	2.5
KL44-08	92.1	95.1	0.211		2110	1.2	20.9	691	343	630	252	220	9	50	47.1	123	0.34
KL44-08	95.1	98.1	0.0211		211	0.51	6.1	1210	680	360	34	20	4	16	3.7	70	0.39
KL44-08	98.1	100.2	0.103		1030	0.44	6.6	2600	350	350	27	80	2	18	6.9	34	0.35
KL44-08	100.2	101.1	0.195		1950	0.52	9.3	1640	690	630	79	384	1	33	6.2	45	0.55
KL44-08	101.1	104	0.077		770	0.46	7.3	5700	780	500	810	142	4	26	8.8	50	0.45
KL44-08	104	106.8	0.0059		59	0.26	3.2	2400	990	250	600	10	2	8	7.0	59	0.19
KL44-08	106.8	109.9	0.0036		36	0.37	4.5	640	134	220	580	2	1	7.9	4.1	32	0.01
KL44-08	109.9	111.7	0.0085		85	0.71	6.9	3720	1350	420	1700	12	1	19.3	11.3	28	0.23
KL44-08	111.7	113.1	0.0237		237	0.72	6	13700	930	420	1370	67	8	15	36.8	41	0.15
KL44-08	113.1	116.1	0.45		4500	0.73	11.7	147500	850	200	1930	107	76	15	257.0	67	0.14
KL44-08	116.1	118.7	0.0297		297	0.31	3.8	12000	1050	83	177	22	7	6.3	35.9	24	0.2
KL44-08	118.7	119.7	0.0096		96	0.17	1.5	1700	212	54	28	3	1	4.7	6.3	20	0.31
KL44-08	119.7	122.1	0.0063		63	0.13	1.3	1060	640	69	38	4	1	5.2	8.4	18	0.14
KL44-08	122.1	123.4	0.0024		24	0.09	0.1	389	91	40	69	1	1	1.9	2.7	19	0.01
KL44-08	123.4	125.6	0.0027		27	0.07	0.1	410	201	30	41	2	1	2	4.1	20	0.01
KL44-08	125.6	128.2	0.0068		68	0.14	0.9	660	284	26	167	3	1	6.3	5.4	19	0.1
KL44-08	128.2	131.1	0.0089		89	0.05	0.1	740	58	15	22	2	1	3.5	4.5	26	0.1
KL44-08	131.1	134.3	0.0078		78	0.07	2	810	430	31	173	9	1	2.8	13.5	25	0.01
KL44-08	134.3	137.1	0.0023		23	0.03	0.1	124	47	11	52	2	1	1	2.0	21	0.01
KL44-08	137.1	139.3	0.0284		284	0.1	3.4	1420	357	68	69	22	1	8	17.0	30	0.01
KL44-08	139.3	142.6	0.073		730	1.78	2.2	6300	1470	780	86	18	9	34	8.7	39	0.38
KL44-08	142.6	145.7	0.0095		95	0.15	2.2	1190	710	38	74	8	1	3.3	14.5	30	0.01
KL44-08	145.7	147.4	0.0082		82	0.45	1.8	850	480	130	1400	7	1	7.2	10.3	51	0.11
KL44-08	147.4	150.5	0.0059		59	0.08	1.2	890	347	18	98	3	1	2.8	3.9	29	0.13
KL44-08	150.5	153.6	0.0218		218	0.19	2.6	3020	740	58	93	16	1	4	12.2	29	0.1
KL44-08	153.6	156.5	0.0099		99	0.1	1.9	860	790	25	47	5	1	3.6	8.0	29	0.01
KL44-08	156.5	158.7	0.0092		92	0.16	0.9	680	208	51	61	3	1	2.2	5.5	23	0.1
KL44-08	158.7	161.7	0.049		490	0.35	3.6	5500	1240	170	195	6	6	11	12.5	37	0.14
KL44-08	161.7	163.7	0.0149		149	0.2	2.7	1890	630	35	46	7	1	3.6	12.6	33	0.01
KL44-08	163.7	166.9	0.0215		215	0.22	3.1	2060	560	56	101	14	1	3.5	13.3	29	0.1
KL44-08	166.9	170.1	0.083		830	0.38	2.1	5900	392	290	145	7	1	7.4	12.0	19	0.21
KL44-08	170.1	173	0.0303		303	0.29	2.4	2800	1100	120	99	12	1	5.1	14.0	14	0.16
KL44-08	173	176	0.0221		221	0.25	2	5100	840	130	93	15	1	4	13.5	13	0.12
KL44-08	176	178.1	0.0332		332	0.46	5.1	7800	2170	260	148	17	1	8.3	30.5	13	0.11
KL44-08	178.1	181.1	0.0261		261	0.23	4.3	2950	2060	110	112	22	2	6.7	15.9	27	0.12
KL44-08	181.1	182.7	0.105		1050	0.65	3.2	3400	670	350	89	24	10	15.2	12.3	33	0.15
KL44-08	182.7	184.5	0.0138		138	0.37	1.4	700	254	140	43	7	1	3.2	6.6	14	0.21
KL44-08	184.5	186.5	0.0398		398	0.21	1.6	3550	227	130	110	16	1	8.7	4.3	22	0.13
KL44-08	186.5	188.1	0.0248		248	0.38	2.7	3480	680	250	114	18	1	14.2	9.0	19	0.16
KL44-08	188.1	190.6	0.0184		184	2.01	1.8	3000	590	400	127	16	2	9.6	5.9	26	0.88
KL44-08	190.6	193.6	0.084		840	6.61	6.3	13900	1300	1750	610	82	5	64	16.5	78	1.74
KL44-08	193.6	197.1	0.214		2140	0.55	1.1	1980	49	340	348	4	15	3.7	15.3	35	0.18
KL44-08	197.1	200.1	1.43		14300	1.16	4.8	40500	2140	860	110	42	151	12.9	124.0	90	0.42
KL44-08	200.1	203.1	0.067		670	0.6	1.8	6800	740	370	57	21	11	10.3	5.8	27	0.1
KL44-08	203.1	206.1	0.25		2500	0.53	1.6	12200	409	250	15	8	16	11.9	15.5	50	0.1
KL44-08	206.1	208.1	0.28		2800	1.84	2.3	2000	660	1100	146	26	20	36	12.3	42	0.21
KL44-08	208.1	210.5	0.044		440	0.15	1.7	640	180	50	234	7	1	4.4	13.3	32	0.01
KL44-08	210.5	213.9	0.012		120	0.79	0.8	1970	1300	270	8	8	1	14	7.5	21	0.01
KL44-08	213.9	215.1	0.202		2020	1.14	1.3	28600	210	680	27	6	60	20	18.0	73	0.19
KL44-08	215.1	217.3	1.89		18900	1.12	3.7	1160	298	360	710	2	34	5.6	42.5	45	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL44-08	217.3	219.3	0.36	3600	0.5	1.2	1160	95	150	1280	4	14	3.7	10.5	22	0.01
KL44-08	219.3	221.1	0.64	6400	0.58	1.3	470	97	100	1990	2	22	2.2	11.8	32	0.01
KL44-08	221.1	224.1	0.137	1370	0.2	0.6	289	69	64	1940	7	9	1.8	9.8	39	0.01
KL44-08	224.1	227.1	0.146	1460	0.23	1	430	38	47	1750	5	101	2.5	39.7	30	0.01
KL44-08	227.1	230.1	0.61	6100	1.46	6.3	720	71	990	695	5	63	20	11.3	39	0.3
KL44-08	230.1	232.1	0.46	4600	1.24	4.9	1100	116	1180	346	4	23	28	8.0	50	0.25
KL44-08	232.1	235.1	0.37	3700	1.17	6.9	3650	181	860	360	18	39	35	14.3	34	0.45
KL44-08	235.1	237.3	0.36	3600	1.12	7	3680	178	900	354	17	40	37	14.5	36	0.45
KL44-08	237.3	240	0.0392	392	0.36	1.1	1220	138	240	200	12	4	12.3	4.3	34	0.25
KL44-08	240	242.5	0.056	560	0.34	1.1	7500	240	200	78	5	13	9.5	4.5	52	0.01
KL44-08	242.5	244.5	0.0113	113	0.18	3.2	1820	520	82	89	23	1	5.6	16.3	29	0.1
KL44-08	244.5	246.5	0.0138	138	0.15	1.2	1240	355	63	81	6	1	5.2	8.1	28	0.01
KL44-08	246.5	249.5	0.0049	49	0.31	1.6	1350	420	62	74	5	1	4.6	10.5	28	0.1
KL44-08	249.5	252.7	0.0091	91	0.2	1.7	1925	920	53	46	6	1	3.6	14.3	19	0.14
KL44-08	252.7	255.4	0.0183	183	0.34	2.4	2600	1120	80	95	11	1	5.2	15.8	34	0.01
KL44-08	255.4	257.1	0.0082	82	0.19	1	1380	318	52	70	6	1	4.8	8.7	19	0.01
KL44-08	257.1	259.5	0.0186	186	0.25	1.3	1910	420	72	49	11	1	6.4	12.5	18	0.18
KL44-08	259.5	262.6	0.0129	129	0.55	3.8	1970	1510	370	43	12	1	14.2	33.6	23	0.26
KL44-08	262.6	265.7	0.0087	87	0.24	0.1	700	580	55	26	4	1	3.9	14.3	17	0.12
KL44-08	265.7	268.8	0.0077	77	0.56	0.6	560	145	66	12	2	1	8	4.5	14	0.36
KL44-08	268.8	271.9	0.0127	127	0.15	0.1	1010	227	25	24	5	1	4.1	6.0	18	0.18
KL44-08	271.9	275	0.0038	38	0.14	0.1	770	405	20	8	4	1	3.1	8.0	16	0.1
KL44-08	275	278.1	0.0037	37	0.15	0.1	263	120	24	10	1	1	4	2.2	17	0.13
KL44-08	278.1	281.1	0.0235	235	0.22	0.7	910	88	33	48	9	1	5.3	7.0	16	0.18
KL44-08	281.1	284.1	0.0077	77	0.16	0.1	470	82	21	34	4	1	2.8	3.5	10	0.15
KL44-08	284.1	287.1	0.0036	36	0.28	0.1	182	113	31	23	5	1	3.8	4.8	16	0.3
KL44-08	287.1	290.1	0.0098	98	0.21	0.1	620	760	23	23	3	1	2.8	23.3	18	0.28
KL44-08	290.1	293.1	0.056	560	0.25	2.1	3050	166	55	148	9	6	4.8	6.0	13	0.32
KL44-08	293.1	296.1	0.085	850	0.08	0.1	1020	53	19	189	58	4	1.7	6.8	16	0.01
KL44-08	296.1	299.1	0.095	950	0.14	0.1	840	143	26	296	27	5	2	11.0	28	0.11
KL44-08	299.1	302.1	0.29	2900	0.32	14.7	12900	5600	67	450	107	26	6.2	105.0	38	0.24
KL44-08	302.1	305.1	0.125	1250	0.56	1.6	690	58	50	200	79	3	2.2	4.7	31	0.01
KL44-08	305.1	308.1	0.135	1350	0.12	0.5	2300	38	76	680	21	7	3.8	7.0	19	0.4
KL44-08	308.1	311.1	0.203	2030	0.82	1.1	6300	33	180	400	26	12	5.8	13.3	30	0.34
KL44-08	311.1	314.1	0.21	2100	0.93	2.1	20500	67	120	215	30	16	4.6	25.5	31	0.32
KL44-08	314.1	317.1	0.095	950	0.55	0.1	2170	77	48	75	52	3	6.5	7.8	35	0.3
KL44-08	317.1	320.1	0.0196	196	0.2	0.1	520	49	24	24	7	1	2.8	4.0	20	0.22
KL44-08	320.1	323.1	0.0041	41	0.19	0.1	105	17	26	8	0.01	1	1.9	1.9	19	0.14
KL44-08	323.1	326.1	0.48	4800	0.53	3.4	10000	374	38	151	2	32	3.9	11.2	20	0.18
KL44-08	326.1	329.1	0.0041	41	0.23	0.1	121	17	34	4	0.01	3	2.9	1.4	16	0.15
KL44-08	329.1	332.1	0.0024	24	0.1	0.1	32	12	59	3	0.01	1	1.2	0.0	18	0.01
KL44-08	332.1	335.1	0.0161	161	0.26	0.1	46	10	72	69	35	1	2.3	1.8	23	0.01
KL44-08	335.1	338.1	0.0055	55	0.12	0.1	149	10	36	10	3	1	1.7	1.7	16	0.01
KL44-08	338.1	341.1	0.0015	15	0.07	0.1	43	11	29	2	0.01	1	0.9	0.8	16	0.01
KL44-08	341.1	344.1	0.0019	19	0.05	0.1	46	10	18	2	0.01	1	1.1	1.1	15	0.01
KL44-08	344.1	347.1	0.0027	27	0.21	0.1	60	15	42	11	0.01	1	4.4	2.8	33	0.11
KL44-08	347.1	350.1	0.0016	16	0.29	0.1	26	12	48	3	0.01	1	5.2	1.7	20	0.15
KL44-08	350.1	353.1	0.001	10	0.01	0.1	19	13	19	2	0.01	1	0.5	0.8	15	0.01
KL44-08	353.1	356.1	0.0025	25	0.01	0.1	90	34	13	3	0.01	1	0.5	0.8	16	0.01
KL44-08	356.1	359.1	0.001	10	0.01	0.1	34	9	16	3	0.01	3	0.5	0.5	15	0.01
KL44-08	359.1	362.1	0.0025	25	0.01	0.1	35	7	10	5	0.01	1	0.4	1.7	14	0.01
KL44-08	362.1	365.1	0.0012	12	0.01	0.1	20	5	15	3	0.01	1	0.6	1.5	13	0.01
KL44-08	365.1	368.1	0.0038	38	0.01	0.1	36	9	30	12	0.01	1	0.6	1.7	16	0.01
KL44-08	368.1	371.1	0.0066	66	0.03	0.1	62	17	19	34	3	2	1	1.9	16	0.01
KL44-08	371.1	374.1	0.0017	17	0.02	0.1	30	12	20	6	0.01	1	1	1.5	18	0.01
KL44-08	374.1	377.1	0.0285	285	0.03	0.1	32	5	15	99	0.01	1	0.6	1.7	17	0.01
KL44-08	377.1	380.1	0.0034	34	0.01	0.1	35	7	14	15	0.01	1	0.5	0.7	16	0.01
KL44-08	380.1	383.1	0.0135	135	0.07	0.1	42	8	26	38	0.01	1	1.4	1.8	19	0.01
KL44-08	383.1	385.3	0.0036	36	0.01	0.1	24	9	14	27	0.01	1	0.3	0.0	12	0.01
KL44-08	385.3	388.4	0.0059	59	0.01	0.1	34	11	5	11	0.01	1	0.2	0.8	12	0.01
KL44-08	388.4	391.4	0.005	50	0.01	0.1	30	7	10	10	0.01	1	0.2	1.1	14	0.01
KL44-08	391.4	394.3	0.001	10	0.01	0.1	46	7	17	2	0.01	1	0.4	0.5	11	0.01
KL44-08	394.3	397.4	0.0096	96	0.01	0.1	31	10	24	11	0.01	3	0.5	0.8	12	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL44-08	397.4	400.5	0.0085		85	0.02	0.1	34	7	23	9	3	3	1.4	0.9	13	0.01
KL44-08	400.5	403.6	0.0146		146	0.02	0.1	51	12	31	8	4	1	0.5	0.0	16	0.01
KL44-08	403.6	406.7	0.0159		159	0.01	0.1	149	11	24	6	0.01	3	0.4	0.0	16	0.01
KL44-08	406.7	409.9	0.0107		107	0.01	0.1	180	13	31	7	1	3	1.5	0.6	19	0.01
KL44-08	409.9	413.1	0.0259		259	0.06	0.1	153	14	72	31	2	4	2.3	1.5	32	0.01
KL44-08	413.1	416.1	0.0194		194	0.12	0.1	1160	22	63	43	6	4	1.3	1.8	31	0.01
KL44-08	416.1	418.7	0.0041		41	0.04	0.1	66	15	53	5	0.01	1	1.7	0.8	19	0.01
KL44-08	418.7	421.8	0.0047		47	0.02	0.1	56	13	30	6	1	1	1.8	0.5	16	0.01
KL44-08	421.8	424.7	0.0119		119	0.04	0.1	75	10	42	12	12	2	1.1	0.5	19	0.01
KL44-08	424.7	427.6	0.0038		38	0.03	0.1	46	10	25	2	1	1	0.6	0.0	16	0.01
KL44-08	427.6	430.6	0.0074		74	0.05	0.1	77	9	54	5	2	1	0.7	0.0	18	0.01
KL44-08	430.6	433.7	0.0065		65	0.05	0.1	53	8	47	4	1	2	1.3	0.0	15	0.01
KL44-08	433.7	436.8	0.0103		103	0.02	0.1	66	8	45	10	4	2	0.4	0.0	20	0.01
KL44-08	436.8	439.9	0.0113		113	0.02	0.1	92	9	18	2	2	1	0.3	0.0	13	0.01
KL44-08	439.9	442.8	0.0048		48	0.04	0.1	98	16	19	3	1	1	0.3	0.0	17	0.01
KL44-08	442.8	445.9	0.0067		67	0.04	0.1	67	7	30	2	1	1	0.4	0.0	21	0.01
KL44-08	445.9	449	0.059		590	1.96	0.8	237	11	25	224	136	3	0.7	3.6	28	0.01
KL44-08	449	451.8	0.147		1470	0.3	1.1	480	29	78	148	125	7	1.7	5.7	41	0.01
KL44-08	451.8	454.9	0.0112		112	0.06	0.1	70	13	40	74	5	1	1.2	0.6	28	0.01
KL44-08	454.9	458	0.008		80	0.01	0.1	37	8	17	3	0.01	1	0.2	0.0	23	0.01
KL44-08	458	461	0.0075		75	0.03	0.1	72	12	31	3	2	1	0.3	0.0	26	0.01
KL44-08	461	463.3	0.077		770	0.9	0.1	74	13	19	352	129	1	0.3	3.5	25	0.01
KL44-08	463.3	466.3	0.026		260	0.06	0.1	289	22	35	12	3	2	0.6	1.4	26	0.01
KL44-08	466.3	469.1	0.19		1900	0.21	1.2	125	16	45	43	7	3	1.2	2.8	23	0.01
KL44-08	469.1	472.4	0.0119		119	0.1	0.1	66	11	70	17	5	1	1.2	0.8	40	0.01
KL44-08	472.4	475.5	0.0315		315	0.05	0.1	60	10	67	36	0.01	1	0.8	0.9	37	0.01
KL44-08	475.5	478.6	0.0095		95	0.03	0.1	45	9	65	47	0.01	1	0.9	0.5	36	0.01
KL44-08	478.6	481.7	0.0013		13	0.01	0.1	51	10	36	3	0.01	1	0.6	2.1	20	0.01
KL44-08	481.7	484.8	0.0011		11	0.02	0.1	38	19	32	2	0.01	1	1.3	1.0	18	0.01
KL44-08	484.8	487.5	0.002		20	0.02	0.1	27	15	55	1	0.01	1	1.8	2.4	18	0.01
KL44-08	487.5	490.6	0.001		10	0.01	0.1	22	8	23	1	0.01	1	0.7	1.2	16	0.01
KL44-08	490.6	493.7	0.0032		32	0.02	0.1	133	200	11	2	0.01	1	0.7	1.4	19	0.01
KL44-08	493.7	496.8	0.0014		14	0.02	0.1	25	12	24	2	0.01	1	1	1.6	21	0.01
KL44-08	496.8	499.9	0.0013		13	0.02	0.1	58	24	42	3	0.01	1	0.8	1.5	18	0.01
KL44-08	499.9	503	0.014		140	0.18	0.1	163	27	200	1130	2	8	3.1	3.9	40	0.13
KL44-08	503	506.1	0.064		640	0.23	0.1	184	43	160	740	6	15	4.5	5.9	89	0.1
KL44-08	506.1	509	0.0277		277	0.59	0.7	163	24	240	1120	7	10	7.5	4.5	75	0.21
KL44-08	509	511.5	0.054		540	0.48	0.8	328	67	360	2970	7	12	10.8	6.5	122	0.39
KL44-08	511.5	514.6	0.083		830	1.49	1.6	388	49	590	1480	8	14	32	7.6	76	1.26
KL44-08	514.6	517.4	0.091		910	0.93	1.6	73	29	260	63	9	4	15.5	6.8	175	0.3
KL44-08	517.4	520.5	0.048		480	1.03	1.2	49	22	220	53	8	4	6.9	5.1	120	0.1
KL44-08	520.5	523.6	0.149		1490	0.63	1.5	81	18	560	29	4	5	22	6.1	63	0.14
KL44-08	523.6	525.2	0.109		1090	0.84	0.9	169	21	540	35	3	7	8.9	5.4	57	0.18
KL44-08	525.2	528.2	0.0287		287	0.18	0.1	880	102	130	23	16	3	4.9	5.3	27	0.1
KL44-08	528.2	530.1	0.0038		38	0.49	0.1	170	22	110	6	0.01	1	7.1	7.6	24	0.23
KL44-08	530.1	533.1	0.0033		33	0.15	1	113	17	77	4	1	1	3.4	5.2	21	0.1
KL44-08	533.1	536.1	0.008		80	0.02	0.1	23	12	40	3	0.01	1	2.3	1.6	17	0.01
KL44-08	536.1	539.1	0.0024		24	0.05	0.1	66	14	48	2	0.01	1	1.5	1.6	16	0.01
KL44-08	539.1	542.1	0.0019		19	0.04	0.1	41	13	35	3	0.01	1	1.2	1.4	17	0.01
KL44-08	542.1	545.1	0.0023		23	0.02	0.1	22	13	20	3	0.01	1	1.1	1.1	16	0.01
KL44-08	545.1	548.1	0.0235		235	0.26	0.5	24	14	120	5	2	1	5.5	2.4	17	0.01
KL44-08	548.1	550.3	0.0242		242	0.91	2.3	94	299	140	1700	168	8	9.9	19.5	58	0.01
KL44-08	550.3	553.4	0.0244		244	0.12	0.1	37	17	54	22	3	18	1.4	2.7	31	0.01
KL44-08	553.4	556.6	0.057		570	0.3	1.4	51	53	110	115	14	11	1.7	7.0	76	0.01
KL44-09	0	2.5	0.0048		48	0.01	0.1	24	16	6	2	0.01	1	0.2	0.5	23	0.01
KL44-09	2.5	5.5	0.0015		15	0.02	0.1	79	37	10	3	0.01	1	0.7	1.6	21	0.01
KL44-09	5.5	8.3	0.0036		36	0.59	4.6	460	119	40	2	0.01	1	5.1	3.8	25	1.43
KL44-09	8.3	9.8	0.0016		16	0.04	1	189	63	17	1	0.01	1	1	1.4	28	0.01
KL44-09	9.8	11.5	0.0085		85	0.01	14.5	197	75	14	5	0.01	1	1.1	2.3	20	0.01
KL44-09	11.5	14.5	0.0022		22	0.01	1.7	198	81	15	4	0.01	1	0.7	1.4	26	0.01
KL44-09	14.5	17.5	0.0046		46	0.03	10.3	5100	990	25	8	0.01	1	5.3	17.0	18	0.3
KL44-09	17.5	20.5	0.0013		13	0.01	0.1	46	20	8	3	0.01	1	0.4	1.3	21	0.01
KL44-09	20.5	23.5	0.001		10	0.01	1	57	43	15	4	0.01	1	0.3	1.1	29	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL44-09	23.5	26.5	0.0029		29	0.01	8	870	1030	26	3	0.01	1	3.7	0.7	30	0.01
KL44-09	26.5	29.5	0.0012		12	0.01	2	118	62	9	2	0.01	1	0.3	0.5	31	0.01
KL44-09	29.5	32.5	0.001		10	0.01	0.1	22	22	6	1	0.01	1	0.01	0.0	24	0.01
KL44-09	32.5	35.5	0.0012		12	0.01	0.1	113	90	6	1	0.01	1	0.8	2.0	23	0.01
KL44-09	35.5	38.5	0.0124		124	0.74	18	11200	10400	210	1	0.01	1	22	210.0	27	0.91
KL44-09	38.5	41.5	0.0017		17	0.03	0.1	440	357	18	1	0.01	1	1.6	5.7	20	0.01
KL44-09	41.5	44.5	0.0018		18	0.02	0.1	135	123	11	2	0.01	1	0.9	3.0	20	0.01
KL44-09	44.5	47.5	0.0103		103	0.33	7.2	970	1200	170	33	7	1	31	7.8	36	0.54
KL44-09	47.5	50.5	0.0075		75	0.14	2.3	267	134	58	1	1	1	7	3.0	30	0.38
KL44-09	50.5	53.5	0.0063		63	0.24	4.6	1130	570	69	1	1	1	14	6.1	27	0.55
KL44-09	53.5	56.5	0.0265		265	0.3	17.8	870	640	210	2	0.01	1	18	8.9	41	0.66
KL44-09	56.5	59.5	0.0041		41	0.11	5.5	640	157	66	4	0.01	1	4.2	4.0	26	0.36
KL44-09	59.5	62.5	0.0012		12	0.04	0.7	87	95	29	1	0.01	1	1.1	2.8	24	0.01
KL44-09	62.5	65.5	0.0023		23	0.05	1	115	80	16	5	0.01	1	1.3	3.2	24	0.13
KL44-09	65.5	68.5	0.0038		38	0.25	2.6	87	71	55	1	0.01	1	4.2	5.2	25	0.45
KL44-09	68.5	71.5	0.003		30	0.27	2.1	520	266	76	3	0.01	1	5.5	7.5	36	0.68
KL44-09	71.5	74.5	0.0033		33	0.11	0.1	205	181	35	2	0.01	1	1.6	3.8	30	0.1
KL44-09	74.5	77.5	0.0018		18	0.38	0.8	121	167	160	2	3	1	3.8	6.4	28	0.17
KL44-09	77.5	80.5	0.0034		34	0.04	0.1	49	59	24	1	0.01	1	0.6	2.9	18	0.01
KL44-09	80.5	83.5	0.003		30	0.1	1.1	312	254	28	3	2	1	1.9	1.2	31	0.29
KL44-09	83.5	86.5	0.0032		32	0.08	0.8	237	193	61	2	1	1	1.5	1.3	30	0.1
KL44-09	86.5	89.5	0.002		20	0.05	0.6	266	156	62	1	2	2	1.4	1.0	20	0.01
KL44-09	89.5	91.6	0.0079		79	0.14	1	520	92	100	3	3	1	2.4	2.3	31	0.13
KL44-09	91.6	93	0.001		10	0.28	0.1	164	21	160	4	0.01	1	3.7	0.6	56	0.01
KL44-09	93	95.5	0.0086		86	0.18	1.1	1080	358	150	22	0.01	1	10.7	1.7	60	0.39
KL44-09	95.5	97.8	0.0118		118	0.22	0.9	184	63	120	24	2	3	5.8	10.3	140	0.11
KL44-09	97.8	99.8	0.0203		203	0.08	0.9	288	78	34	18	0.01	1	3	3.5	111	0.28
KL44-09	99.8	101.4	0.047		470	0.61	14.5	3980	920	210	36	7	2	46	33.3	83	3.3
KL44-09	101.4	104.5	0.24		2400	0.85	58	6200	6000	1430	40	116	9	165	77.5	75	5.58
KL44-09	104.5	107.4	0.0399		399	2.56	13.8	5800	2400	200	24	34	1	24	9.5	82	4.9
KL44-09	107.4	110.5	0.107		1070	0.51	2.9	2070	600	61	64	4	4	7.5	1.3	48	1.01
KL44-09	110.5	113.5	0.0171		171	0.23	1.7	1350	420	47	23	4	1	10.2	1.5	37	0.33
KL44-09	113.5	116.5	0.0043		43	0.26	0.7	960	233	55	23	1	1	3.5	1.7	153	0.1
KL44-09	116.5	119.5	0.0027		27	0.1	1.2	740	221	120	73	4	3	5.6	1.3	202	0.01
KL44-09	119.5	122.5	0.0346		346	0.27	3	1440	1340	350	50	20	8	40	7.8	276	0.19
KL44-09	122.5	125.5	0.0026		26	0.16	2.1	1180	345	170	69	14	4	10.3	3.3	191	0.17
KL44-09	125.5	128.5	0.0034		34	0.04	0.9	440	211	120	126	1	3	6.6	3.8	69	0.01
KL44-09	128.5	131.5	0.0057		57	0.03	1.4	450	246	29	430	4	3	4	3.0	21	0.01
KL44-09	131.5	134.5	0.0195		195	0.35	2.1	11300	1500	260	670	3	4	70	8.8	50	1.08
KL44-09	134.5	137.5	0.109		1090	0.76	11	7100	3000	660	570	75	7	120	25.2	116	1.01
KL44-09	137.5	140.5	0.0112		112	0.05	1	680	125	46	39	3	1	7.4	2.5	30	0.01
KL44-09	140.5	143.5	0.0156		156	0.12	2.7	3660	1930	56	100	6	3	13	10.5	31	0.14
KL44-09	143.5	146.5	0.0042		42	0.06	0.8	750	316	21	23	2	2	5	5.0	20	0.01
KL44-09	146.5	149.5	0.0094		94	0.04	0.8	860	211	33	29	3	2	4.5	5.3	25	0.1
KL44-09	149.5	151.7	0.0041		41	0.02	0.9	217	231	13	45	6	2	1.5	3.3	23	0.01
KL44-09	151.7	153.5	0.0057		57	0.05	2.2	770	590	36	76	7	3	6.5	9.3	21	0.01
KL44-09	153.5	155.5	0.0028		28	0.28	0.8	395	214	25	16	3	2	2.6	4.0	22	0.01
KL44-09	155.5	158.5	0.0038		38	0.1	0.8	430	355	45	26	3	2	2.7	2.9	41	0.01
KL44-09	158.5	160.2	0.0089		89	0.1	3.5	950	610	43	21	36	1	2.5	9.5	36	0.01
KL44-09	160.2	161.9	0.0042		42	0.07	1.5	370	460	16	25	7	1	1.4	3.3	24	0.01
KL44-09	161.9	164.9	0.0044		44	0.05	2	217	460	15	41	9	1	1.1	5.0	28	0.01
KL44-09	164.9	167	0.0027		27	0.05	2.1	310	650	23	37	7	1	1.2	3.5	27	0.01
KL44-09	167	169.6	0.006		60	0.19	5.4	1720	1930	52	31	22	1	5.5	10.0	26	0.01
KL44-09	169.6	172.5	0.0241		241	0.13	3.3	760	700	120	58	20	1	18.5	9.8	27	0.01
KL44-09	172.5	173.9	0.0318		318	0.62	7	2010	890	210	266	66	4	18.8	19.7	58	0.11
KL44-09	173.9	175.8	0.0127		127	0.24	4.8	1090	730	79	102	30	2	7	10.8	41	0.01
KL44-09	175.8	178.9	0.0105		105	0.13	12.4	1920	1550	39	30	56	1	7.8	12.0	33	0.01
KL44-09	178.9	181.3	0.0054		54	0.07	2.9	650	670	29	35	13	1	3	6.8	32	0.01
KL44-09	181.3	182.5	0.072		720	0.19	5	1150	1260	270	76	16	1	36	12.0	29	0.11
KL44-09	182.5	184.1	0.0128		128	0.08	3.2	660	1330	53	38	7	1	9.3	9.0	15	0.01
KL44-09	184.1	185.5	0.0098		98	0.06	1.7	790	1240	37	26	4	1	2.8	6.3	10	0.01
KL44-09	185.5	188.5	0.0165		165	0.1	6.7	5000	3200	46	34	18	1	4	19.2	18	0.01
KL44-09	188.5	191.5	0.0024		24	0.04	0.8	289	268	10	15	3	1	1.5	2.5	9	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL44-09	191.5	193.6	0.0065	65	0.03	0.8	276	172	24	15	4	1	1.7	3.3	9	0.01
KL44-09	193.6	195.1	0.076	760	0.09	1.7	530	217	270	26	5	3	23	4.0	12	0.01
KL44-09	195.1	198	0.011	110	0.04	3.8	1720	1580	25	26	22	1	3.7	14.7	15	0.01
KL44-09	198	201	0.0084	84	0.03	1.6	1140	640	20	33	7	1	1.4	7.0	13	0.01
KL44-09	201	203.1	0.0071	71	0.03	2	700	600	19	21	6	1	1.4	8.0	12	0.01
KL44-09	203.1	206.1	0.121	1210	0.26	42	68000	26900	81	12	118	2	9.3	175.0	22	0.35
KL44-09	206.1	207.7	0.0245	245	0.07	8.8	7000	4900	22	10	26	1	2.9	36.7	16	0.1
KL44-09	207.7	209.5	0.167	1670	0.23	33	22000	10100	240	59	152	1	40	114.0	22	0.1
KL44-09	209.5	212.5	0.36	3600	0.36	6.9	25200	800	660	268	72	31	70	82.5	55	0.1
KL44-09	212.5	215.5	1.04	10400	0.59	14.5	79000	860	1620	592	66	46	50	66.0	48	0.36
KL44-09	215.5	218.5	0.54	5400	0.64	10.3	20100	350	500	564	34	18	18.3	54.7	62	0.1
KL44-09	218.5	221.5	0.51	5100	0.83	12.5	51500	580	350	890	204	21	5.3	76.0	49	0.12
KL44-09	221.5	224.3	0.65	6500	1.11	38	70000	2000	1110	490	1510	19	40	179.0	90	0.15
KL44-09	224.3	226	0.57	5700	0.87	12.6	40000	215	490	577	109	9	9.5	73.0	109	0.1
KL44-09	226	228.5	2.57	25700	2.76	35	23000	174	2800	581	256	4	10.8	45.0	40	0.19
KL44-09	228.5	232.5	1.5	15000	2.24	28.1	25500	300	2100	910	830	8	30	84.0	59	0.15
KL44-09	232.5	233.5	0.29	2900	0.54	6.9	15900	171	290	790	140	2	6	30.0	32	0.01
KL44-09	233.5	236.1	0.305	3050	0.31	5.4	3770	178	69	135	52	2	0.7	16.4	18	0.01
KL44-09	236.1	239.2	0.155	1550	0.32	3.4	3000	126	40	52	18	2	1	14.0	18	0.01
KL44-09	239.2	242.3	0.179	1790	0.26	2.6	2720	293	62	24	10	4	2.1	10.0	25	0.01
KL44-09	242.3	245.4	0.095	950	0.16	1.7	3460	314	280	20	5	9	6.5	8.8	26	0.01
KL44-09	245.4	248.5	0.199	1990	0.27	3.5	2920	1400	450	16	7	11	5	15.0	22	0.01
KL44-09	248.5	251.5	0.21	2100	0.26	3.3	2060	161	340	31	11	10	4.2	13.7	28	0.1
KL44-09	251.5	254.5	0.34	3400	0.49	4.5	9200	146	820	21	4	21	8.3	15.3	35	0.16
KL44-09	254.5	257.5	0.3	3000	0.4	3.2	7200	120	920	31	7	11	11.3	12.0	37	0.59
KL44-09	257.5	260.5	0.44	4400	0.85	5.1	18100	510	1710	38	42	18	40	14.7	43	1.56
KL44-09	260.5	263.5	0.75	7500	1.21	6.8	5600	860	2600	38	4	24	130	21.3	80	2.56
KL44-09	263.5	266.5	0.69	6900	0.64	1.8	3400	146	1860	22	2	41	15.5	40.1	116	0.74
KL44-09	266.5	269.5	0.81	8100	0.82	1.6	1360	90	820	17	0.01	40	8	20.5	73	0.16
KL44-09	269.5	272.5	0.76	7600	0.78	1.3	6600	320	1180	92	0.01	25	6.8	11.4	92	0.35
KL44-09	272.5	275.5	0.57	5700	0.7	1.2	3200	750	1350	13	1	30	24	16.9	130	0.52
KL44-09	275.5	278.5	0.82	8200	0.56	2	1300	405	490	28	4	30	6.5	12.0	62	0.15
KL44-09	278.5	281.5	0.84	8400	0.64	2.1	4500	530	1140	80	0.01	28	5	15.5	103	0.27
KL44-09	281.5	284.5	0.76	7600	0.67	3.1	2700	183	910	53	0.01	20	5.8	10.8	182	0.76
KL44-09	284.5	287.5	0.93	9300	0.57	2	160	164	46	108	2	30	4.5	14.5	174	0.18
KL44-09	287.5	290.5	0.73	7300	0.44	2.9	1880	630	1080	1500	0.01	16	3.6	7.9	98	0.41
KL44-09	290.5	293.5	0.175	1750	0.13	1.1	1580	1500	240	560	0.01	6	0.9	4.5	235	0.26
KL44-09	293.5	296.5	0.162	1620	0.47	1.4	3590	1530	370	1925	0.01	12	2.2	9.4	173	0.3
KL44-09	296.5	299.5	0.454	4540	0.26	1.7	800	145	56	188	0.01	17	2.2	9.5	49	0.01
KL44-09	299.5	302.1	0.135	1350	0.16	0.6	940	237	83	440	0.01	9	3.3	4.8	54	0.01
KL44-09	302.1	305.1	0.143	1430	0.12	0.1	670	74	63	560	0.01	6	2.3	2.5	52	0.01
KL44-09	305.1	308.1	0.53	5300	0.32	1.6	185	21	38	168	0.01	15	2.1	7.3	46	0.01
KL44-09	308.1	311.3	0.487	4870	0.34	1.9	160	28	11	42	0.01	14	0.3	8.8	17	0.01
KL44-09	311.3	314.3	0.67	6700	0.35	2	155	16	31	170	0.01	20	2.3	9.0	54	0.01
KL44-09	314.3	317.4	0.94	9400	0.52	2.3	180	36	20	762	0.01	20	0.7	12.0	30	0.01
KL44-09	317.4	320.5	0.214	2140	0.18	1	60	22	14	1370	0.01	11	1.2	5.3	55	0.01
KL44-09	320.5	323.5	0.415	4150	0.33	1.4	260	213	28	1270	0.01	19	1.1	8.5	31	0.01
KL44-09	323.5	326.5	1.4	14000	0.75	3.1	155	66	11	540	0.01	27	0.9	16.0	26	0.01
KL44-09	326.5	329.5	0.66	6600	0.42	1.4	50	23	24	43	2	12	0.3	7.0	105	0.01
KL44-09	329.5	332.5	0.97	9700	0.6	3.9	154	21	19	225	0.01	17	1.9	16.0	26	0.01
KL44-09	332.5	335.5	0.304	3040	0.19	1.7	171	17	7	265	0.01	11	0.4	7.0	18	0.01
KL44-09	335.5	338.5	0.419	4190	0.3	2.1	384	52	36	72	0.01	15	1.4	7.5	72	0.01
KL44-09	338.5	340.5	0.82	8200	0.31	1.2	54	46	24	88	3	20	0.2	12.0	87	0.01
KL44-09	340.5	344	0.198	1980	0.33	1	3380	440	140	140	1	11	2.6	6.3	117	0.1
KL44-09	344	346.8	0.36	3600	0.44	1.4	9010	910	350	457	0.01	34	2.1	8.0	122	0.01
KL44-09	346.8	349.9	1.73	17300	0.92	2.6	3380	630	37	169	0.01	34	0.5	12.0	39	0.01
KL44-09	349.9	352.9	0.403	4030	0.23	1.3	6120	1310	220	206	0.01	13	1.6	7.8	73	0.01
KL44-09	352.9	355.9	0.48	4800	0.44	1.7	14100	4300	360	74	0.01	13	3.5	7.0	108	1.33
KL44-09	355.9	359.5	0.307	3070	0.16	1.2	258	74	17	47	0.01	7	0.5	3.3	40	0.01
KL44-09	359.5	362.5	0.22	2200	0.13	0.7	104	51	13	230	0.01	6	0.01	4.3	37	0.01
KL44-09	362.5	365.5	0.71	7100	0.28	2.2	121	56	24	486	0.01	16	1.8	7.5	67	0.01
KL44-09	365.5	368.5	1.61	16100	0.84	3.7	211	108	7	803	0.01	24	0.5	9.5	51	0.01
KL44-09	368.5	371.5	0.67	6700	0.42	3	2050	680	71	11	10	21	1.5	5.3	20	0.16

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL44-09	371.5	374.5	1.63	16300	0.72	3.3	3170	490	54	130	0.01	28	2	11.0	45	0.01
KL44-09	374.5	377.5	1.67	16700	0.85	3.6	121	30	3	116	0.01	46	0.4	17.0	20	0.01
KL44-09	377.5	380.2	0.72	7200	0.35	2.5	197	86	84	433	1	17	1.9	5.8	60	0.01
KL44-09	380.2	383.3	2.88	28800	1.26	4.8	115	28	6	35	0.01	46	0.6	25.0	23	0.01
KL44-09	383.3	386.4	1	10000	0.6	2.2	145	146	3	23	0.01	21	1.3	7.5	22	0.01
KL44-09	386.4	389.5	2.89	28900	1.21	3.7	243	56	2	6	0.01	30	0.9	18.0	27	0.01
KL44-09	389.5	392.5	0.422	4220	0.26	1.9	115	40	7	15	0.01	13	0.5	4.8	23	0.01
KL44-09	392.5	395.5	0.66	6600	0.28	2.2	307	118	14	21	1	17	1.1	5.3	22	0.01
KL44-09	395.5	398.5	2.02	20200	0.91	4.5	720	241	7	15	2	36	1.9	12.5	24	0.01
KL44-09	398.5	401.5	2.04	20400	0.92	4.4	240	49	10	44	0.01	34	1.6	19.0	23	0.01
KL44-09	401.5	404.5	0.85	8500	0.62	2.6	170	29	17	796	0.01	20	1	10.5	32	0.01
KL44-09	404.5	407.5	0.086	860	0.11	0.8	450	167	18	6	3	14	0.8	2.7	12	0.01
KL44-09	407.5	411.5	2.18	21800	0.91	3.4	112	37	2	48	0.01	31	0.3	20.0	17	0.01
KL44-09	411.5	413.5	0.168	1680	0.17	1.5	630	241	20	10	4	12	0.7	7.2	17	0.01
KL44-09	413.5	416.5	0.354	3540	0.25	2.5	520	176	41	6	2	14	1.5	6.2	20	0.01
KL44-09	416.5	419.5														
KL44-09	419.5	422.5	2.35	23500	1.2	6.5	740	200	8	67	4	60	2.6	13.5	18	0.01
KL44-09	422.5	425.5	1.69	16900	0.8	3.8	480	126	2	17	7	68	1.5	8.0	13	0.01
KL44-09	425.5	428.5	2.8	28000	1.2	5.9	600	171	4	4	3	42	1.3	14.5	17	0.01
KL44-09	428.5	431.5	2.81	28100	2.86	4.2	850	550	8	47	1	37	2.8	16.0	23	0.01
KL44-09	431.5	434.5	1.23	12300	0.62	1.3	346	97	3	9	1	30	2.8	5.5	22	0.01
KL44-09	434.5	437.5	1.74	17400	0.88	3.8	540	1030	13	25	7	28	1.8	13.5	31	0.01
KL44-09	437.5	440.5	0.64	6400	0.4	1	251	221	31	33	2	16	2.8	5.7	24	0.01
KL44-09	440.5	443.5	0.64	6400	0.36	1.2	258	251	10	30	2	20	1	5.9	45	0.01
KL44-09	443.5	446.5														
KL44-09	446.5	449.5	2.72	27200	1.63	4.2	610	137	2	14	2	33	0.3	18.0	31	0.01
KL44-09	449.5	452.5	2.78	27800	2.26	5	650	530	3	14	3	35	0.7	16.0	27	0.01
KL44-09	452.5	455.5	3.85	38500	2.22	5.4	1050	510	3	6	2	42	0.5	10.0	23	0.01
KL44-09	455.5	458.5	2.85	28500	2.42	5	900	375	6	8	2	36	0.7	9.0	27	0.01
KL44-09	458.5	461.5	4.79	47900	4.78	8.6	1220	680	6	8	2	32	0.9	9.0	32	0.01
KL44-09	461.5	464.5	4.6	46000	4.98	9	1210	680	7	10	2	34	0.8	10.0	37	0.01
KL44-09	464.5	467.5	4.59	45900	4.04	8.5	1200	2840	8	7	1	45	1.4	12.0	34	0.01
KL44-09	467.5	470.5	5	50000	4.56	9.6	1720	183	7	7	0.01	42	0.9	9.4	24	0.01
KL44-09	470.5	473.5	2.8	28000	1.66	6.7	1310	560	3	53	1	37	1	10.0	35	0.01
KL44-09	473.5	476.5	2.88	28800	1.96	10.5	2090	2150	2	175	2	31	1.2	6.0	24	0.01
KL44-09	476.5	479.5	3.85	38500	1.72	4.2	1180	286	1	465	2	35	0.7	9.0	24	0.01
KL44-09	479.5	482.5	1.93	19300	0.92	3.1	800	127	4	9	3	30	0.8	10.3	39	0.01
KL44-09	482.5	485.5	0.6	6000	0.3	1.2	63	12	2	33	1	78	0.01	13.8	23	0.01
KL44-09	485.5	488.5	2.31	23100	1.36	17.7	415	40	6	22	32	25	1	31.0	53	0.01
KL44-09	488.5	490.9	2.28	22800	0.5	7.3	192	132	76	25	10	20	0.6	29.0	84	0.01
KL44-09	490.9	493.9	1.65	16500	0.38	3.5	430	365	55	600	7	24	1.1	18.5	116	0.01
KL44-09	493.9	495.5	2.07	20700	0.26	3.5	186	160	24	2170	2	38	0.5	19.0	180	0.01
KL44-09	495.5	497.5	1.85	18500	0.27	1.8	346	1020	20	13700	7	23	0.3	14.5	171	0.01
KL44-09	497.5	500.5	0.454	4540	0.04	0.8	122	71	10	200	2	15	0.5	12.3	227	0.01
KL44-09	500.5	503.5	0.92	9200	0.2	2.1	283	128	40	84	8	16	0.4	18.0	99	0.01
KL44-09	503.5	506.5	1.19	11900	0.28	0.8	311	136	55	173	1	26	0.4	19.3	124	0.01
KL44-09	506.5	509.5	0.79	7900	0.15	1.3	520	122	31	216	1	21	0.2	15.5	90	0.01
KL44-09	509.5	512.5	1.78	17800	0.33	2.1	196	106	18	87	2	36	0.2	21.0	133	0.01
KL44-09	512.5	515.5	1.74	17400	0.32	2.6	222	132	14	506	2	26	0.2	12.0	119	0.01
KL44-09	515.5	518.5	1.46	14600	0.3	2.3	180	129	13	742	3	22	0.3	11.5	128	0.01
KL44-09	518.5	521.6	1.4	14000	0.34	0.9	189	82	16	368	2	20	0.3	14.0	152	0.01
KL44-09	521.6	524.5	1.06	10600	0.46	1.2	181	69	25	226	3	17	0.2	13.0	113	0.01
KL44-09	524.5	527.5														
KL44-09	527.5	530.5	0.82	8200	0.32	0.9	411	183	58	161	1	27	0.6	18.5	99	0.01
KL44-09	530.5	533.5	0.94	9400	0.5	1.5	172	98	25	238	2	25	0.4	14.5	156	0.01
KL44-09	533.5	536.5	1.75	17500	0.51	2.7	212	210	39	112	1	26	3.5	15.0	140	0.01
KL44-09	536.5	539.5	0.78	7800	0.11	3.4	235	103	94	147	19	24	4.3	11.3	177	0.22
KL44-09	539.5	542.5	0.74	7400	0.8	2.2	780	470	53	67	18	25	0.9	18.8	130	0.01
KL44-09	542.5	545.5	0.76	7600	0.48	2.6	86	37	21	46	4	16	0.3	9.5	126	0.01
KL44-09	545.5	548.5	0.85	8500	0.63	2.2	420	113	55	94	6	17	0.6	14.8	119	0.01
KL44-09	548.5	551.5	0.408	4080	0.18	1.2	100	64	25	31	7	14	1	18.2	91	0.01
KL44-09	551.5	553.8	0.69	6900	0.27	1.4	115	148	190	85	6	13	0.4	12.6	127	0.24
KL44-09	553.8	557	1.58	15800	0.48	1.8	115	73	34	131	7	20	0.5	19.5	96	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL44-09	557	560.1	1.33	13300	0.44	3.6	51	15	0.01	274	1	46	0.01	17.0	58	0.01
KL44-09	560.1	563.2	0.71	7100	0.29	1.4	60	28	25	36	4	13	0.3	6.5	115	0.01
KL44-09	563.2	566.5	0.53	5300	0.25	1.9	37	22	22	65	5	12	0.2	6.0	89	0.01
KL44-09	566.5	569.5	1.56	15600	0.46	4.3	88	62	40	59	7	16	0.5	11.5	95	0.01
KL44-09	569.5	572.5	0.438	4380	0.29	1.2	50	27	17	15	10	14	0.01	13.5	124	0.01
KL44-09	572.5	575.5	0.68	6800	0.35	1.4	129	43	47	22	6	13	0.7	13.3	132	0.01
KL44-09	575.5	578.5	0.497	4970	0.16	1.1	185	32	28	54	8	13	0.4	16.7	184	0.01
KL44-09	578.5	581.5	1.8	18000	0.49	5.4	60	16	11	164	4	25	0.01	12.5	81	0.01
KL44-09	581.5	584.5	0.399	3990	0.08	1.3	57	78	58	403	2	15	1.1	12.3	166	0.1
KL44-09	584.5	587.5	0.67	6700	0.29	2.7	70	61	31	573	9	16	5.6	7.3	82	0.01
KL44-09	587.5	590.5	0.509	5090	0.2	1.8	34	9	3	432	5	12	0.3	6.2	79	0.01
KL44-09	590.5	593.5	1.22	12200	0.47	3.1	60	107	30	245	13	33	12.5	9.0	96	0.01
KL44-09	593.5	596.5	0.499	4990	0.17	1.6	43	9	2	530	1	13	0.01	6.1	81	0.01
KL44-09	596.5	599.5	0.496	4960	0.17	1.8	44	7	4	54	3	15	0.01	7.8	88	0.01
KL44-09	599.5	602.5	0.6	6000	0.24	1.5	65	13	3	75	1	13	0.01	7.0	68	0.01
KL44-09	602.5	605.5	0.72	7200	0.32	3.2	63	73	18	461	7	23	7.4	6.3	67	0.01
KL44-09	605.5	608.5	1.54	15400	0.65	7.7	930	182	26	1140	57	22	0.7	10.3	51	0.01
KL44-09	608.5	611.5	1.27	12700	0.55	5.5	95	52	9	5500	4	16	0.2	12.0	56	0.01
KL44-09	611.5	614.5	1.19	11900	0.56	5.5	232	60	18	2580	13	16	0.2	1.5	57	0.01
KL44-09	614.5	617.5	1.3	13000	0.64	6.2	510	96	21	2660	22	18	0.4	10.5	52	0.01
KL44-09	617.5	618.7	2.21	22100	0.63	3.5	264	72	8	6800	2	22	0.5	14.0	83	1.52
KL44-09	618.7	620.5	0.287	2870	0.12	1.4	248	186	19	703	2	12	0.2	16.7	186	0.68
KL44-09	620.5	623.5	0.378	3780	0.28	2.8	680	177	15	26	27	17	0.4	3.5	20	0.01
KL44-09	623.5	626.5	0.295	2950	0.09	1.2	33	106	41	625	4	10	1.2	11.5	139	0.1
KL44-09	626.5	629.5	0.495	4950	0.12	1.5	79	107	360	390	3	16	7.2	15.8	90	0.3
KL44-09	629.5	632.5	0.483	4830	0.21	2.3	1320	1410	400	321	5	23	35	11.8	171	0.86
KL44-09	632.5	635.5	0.54	5400	0.15	2.4	259	248	47	148	4	14	0.8	14.0	136	0.37
KL44-09	635.5	638.5	0.67	6700	0.08	1.9	156	107	260	200	3	15	5.9	10.3	70	0.01
KL44-09	638.5	641.5	0.476	4760	0.12	4.3	210	259	40	177	19	15	1.2	11.3	153	0.39
KL44-09	641.5	644.5	0.084	840	0.05	1.2	102	107	24	139	3	12	0.6	11.8	168	0.1
KL44-09	644.5	647.5	0.289	2890	0.07	2	93	71	170	231	2	13	3.7	16.9	186	0.21
KL44-09	647.5	650.5	0.93	9300	0.13	7	180	72	110	147	50	14	1.4	7.3	170	0.43
KL44-09	650.5	653.5	0.287	2870	0.09	1.6	107	264	16	261	4	16	0.5	13.0	124	0.2
KL44-09	653.5	656.5	0.328	3280	0.18	1.1	68	18	3	7	1	25	3.4	3.9	33	0.01
KL44-09	656.5	659.5	1.14	11400	2.4	5.2	2500	950	3800	165	1	32	14.9	9.5	135	0.75
KL44-09	659.5	662.5	0.65	6500	0.19	1.6	98	56	100	271	3	15	1.6	6.0	74	0.01
KL44-09	662.5	665.5	0.56	5600	0.12	1.2	103	55	7	224	2	18	0.5	10.5	142	0.18
KL44-09	665.5	668.5	0.463	4630	0.12	1	104	53	10	297	2	16	0.01	7.3	116	0.01
KL44-09	668.5	671.5	0.309	3090	0.09	2.3	620	193	23	95	2	13	0.3	9.0	117	0.31
KL44-09	671.5	674.5	0.23	2300	0.07	1.5	710	256	20	143	5	14	0.2	9.5	121	0.18
KL44-09	677.5	680.5	0.61	6100	0.09	1.9	124	122	110	182	3	18	0.4	10.0	148	0.23
KL44-09	680.5	683.5	0.356	3560	0.07	0.8	29	26	2	351	1	19	0.01	9.0	135	0.01
KL44-09	683.5	686.5	0.24	2400	0.05	0.7	110	70	2	354	1	21	0.01	11.0	148	0.01
KL44-09	686.5	689.5	0.165	1650	0.04	0.5	45	31	2	144	1	22	0.01	10.7	195	0.01
KL44-09	689.5	692.5	1.03	10300	0.13	2.2	57	50	13	281	1	27	0.3	14.3	70	0.27
KL44-09	692.5	695.5	1.2	12000	0.39	4	71	43	9	258	4	22	0.2	11.0	153	0.23
KL44-09	695.5	698.5	0.21	2100	0.1	0.8	55	51	18	200	3	16	0.6	8.5	226	0.01
KL44-09	698.5	701.5	0.28	2800	0.09	0.6	46	50	45	420	3	23	1.7	13.8	253	0.01
KL44-09	701.5	704.5	0.31	3100	0.11	0.8	47	48	20	490	2	37	0.6	14.5	155	0.01
KL44-09	704.5	707.5	0.59	5900	0.14	1.4	40	32	21	430	3	33	0.01	10.3	150	0.01
KL44-09	707.5	709	3.41	34100	0.77	11.6	253	1090	480	169	126	20	150	14.5	72	0.01
KL44-09	709	710.5	0.504	5040	0.16	1.8	41	36	33	355	11	26	10.6	7.7	116	0.01
KL44-09	710.5	713.2	0.56	5600	0.08	1	103	54	8	86	1	16	0.4	8.3	138	0.01
KL44-09	713.2	716.3	0.6	6000	0.3	2.7	54	11	2	27	1	43	0.01	8.8	30	0.01
KL44-09	716.3	719.4	0.418	4180	0.2	1.2	58	11	2	30	2	52	0.2	12.5	39	0.01
KL44-09	719.4	722	0.68	6800	0.38	1.8	88	9	3	7	1	50	0.01	7.0	23	0.01
KL44-09	722	725.1	0.66	6600	0.34	2.1	93	8	3	17	1	60	0.2	8.0	20	0.01
KL44-09	725.1	728.2	0.66	6600	0.36	2	87	9	2	7	1	48	0.2	6.8	23	0.01
KL44-09	728.2	731.3	0.187	1870	0.16	0.7	61	27	10	6	1	35	0.6	8.5	35	0.01
KL44-09	731.3	734.4	2.79	27900	0.28	4.5	138	760	30	2100	6	33	0.3	25.5	111	0.01
KL44-09	734.4	737.5	0.05	500	0.04	0.1	53	10	1	4	1	23	0.2	4.8	36	0.01
KL44-09	737.5	740.5	0.112	1120	0.06	0.1	48	11	0.01	6	1	35	0.2	13.0	52	0.01
KL44-09	740.5	743.5	0.76	7600	0.37	1	71	9	3	6	0.01	24	0.2	10.5	25	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL44-09	743.5	746.5	0.81	8100	0.51	1.4	161	21	18	48	0.01	34	3.7	10.3	22	0.01
KL44-09	746.5	749.5	1.15	11500	0.63	2	68	10	0.01	16	1	39	0.2	15.5	32	0.01
KL44-09	749.5	752.5	0.54	5400	0.33	0.8	77	9	1	115	0.01	38	0.5	7.4	30	0.01
KL44-09	752.5	755.5	0.174	1740	0.14	0.7	121	9	1	5	0.01	46	2.5	3.8	23	0.01
KL44-09	755.5	758.5	0.254	2540	0.06	0.7	12	10	2	464	0.01	24	0.3	8.7	101	0.01
KL44-09	758.5	761.5	1.27	12700	0.98	2.1	168	15	1	50	2	53	0.5	12.5	17	0.01
KL44-09	761.5	764.5	0.95	9500	0.57	1.7	99	14	3	19	0.01	22	0.2	16.5	21	0.01
KL44-09	764.5	767.5	0.439	4390	0.28	0.9	98	11	4	12	1	31	0.2	20.5	17	0.01
KL44-09	767.5	770.5	0.061	610	0.01	0.1	21	11	1	30	0.01	2	0.4	3.8	49	0.01
KL44-09	770.5	773.5	0.22	2200	0.14	0.8	69	12	6	26	0.01	15	0.3	6.5	43	0.01
KL44-09	773.5	776.5	1.22	12200	0.96	2.5	115	14	17	14	0.01	35	1.4	12.5	27	0.01
KL44-09	776.5	779.5	0.8	8000	0.44	2.1	45	8	2	71	0.01	22	0.2	11.8	25	0.01
KL44-09	779.5	782.5	1.35	13500	0.84	2.6	140	14	14	37	0.01	35	0.5	13.3	31	0.01
KL44-09	782.5	785.5	0.75	7500	0.29	1.4	98	30	10	108	0.01	14	0.2	9.8	20	0.01
KL44-09	785.5	788.5	0.53	5300	0.09	0.1	16	8	7	412	0.01	28	0.5	8.8	58	0.01
KL44-09	788.5	791.5	0.83	8300	0.36	1.3	82	13	5	136	0.01	18	0.3	9.5	32	0.01
KL44-09	791.5	794.5	0.88	8800	0.61	1.1	70	9	6	156	0.01	19	0.4	9.2	29	0.01
KL44-09	794.5	797.5	0.54	5400	0.33	1.1	69	27	10	8	0.01	10	0.7	6.5	25	0.01
KL44-09	797.5	800.5														
KL44-09	800.5	803.5	0.92	9200	0.76	1.7	70	8	12	27	0.01	14	0.4	9.8	28	0.01
KL44-09	803.5	806.5	0.59	5900	0.33	0.8	48	8	15	35	0.01	9	0.3	9.0	15	0.01
KL44-09	806.5	809.5	0.61	6100	0.39	0.9	93	18	5	8	0.01	16	1.6	5.1	30	0.01
KL44-09	809.5	812.5	1.52	15200	1.11	2.6	294	13	1	10	0.01	58	0.01	7.5	23	0.01
KL44-09	812.5	815.5	0.6	6000	0.25	0.7	53	7	8	362	0.01	27	0.5	8.4	43	0.01
KL44-09	815.5	818.5	0.337	3370	0.23	0.1	64	9	9	11	0.01	16	10.3	2.5	34	0.01
KL44-09	818.5	821.5														
KL44-09	821.5	824.5	0.75	7500	0.39	1.1	84	13	4	217	0.01	25	0.3	7.8	43	0.01
KL44-09	824.5	827.5	0.478	4780	0.21	1.5	53	7	1	33	1	19	0.01	8.5	47	0.01
KL44-09	827.5	830.5	1.14	11400	1.11	1.4	113	10	1	28	0.01	32	0.3	10.0	42	0.01
KL44-09	830.5	833.5	0.92	9200	0.6	1.1	122	7	4	9	0.01	22	0.01	6.0	39	0.01
KL44-09	833.5	836.5	0.386	3860	0.28	0.1	68	9	1	8	0.01	16	0.2	2.8	30	0.01
KL44-09	836.5	839.5	0.327	3270	0.27	0.1	58	7	1	2	0.01	17	0.01	3.3	31	0.01
KL44-09	839.5	842.5	0.152	1520	0.06	0.1	27	6	1	14	0.01	4	0.2	1.5	16	0.01
KL44-09	842.5	845.5	0.102	1020	0.04	0.5	35	9	1	193	1	8	0.01	3.5	19	0.01
KL44-09	845.5	848.5	0.372	3720	0.18	0.9	112	7	0.01	64	1	12	0.2	2.8	28	0.01
KL44-09	848.5	851.5	0.66	6600	0.35	2	220	9	6	18	1	29	0.2	5.0	40	0.01
KL44-09	851.5	854.5	0.269	2690	0.11	1	116	17	17	24	1	11	0.6	9.5	45	0.01
KL44-09	854.5	857.5	0.0016	16	0.01	0.1	22	17	11	4	0.01	2	0.3	1.3	27	0.01
KL44-09	857.5	860.5	0.146	1460	0.08	1	131	12	1	4	0.01	4	0.2	2.3	29	0.01
KL44-09	860.5	863.5	0.043	430	0.01	0.1	53	13	2	4	0.01	3	0.01	1.3	18	0.01
KL44-09	863.5	866.5	0.0223	223	0.01	0.1	29	9	0.01	5	0.01	1	0.01	1.3	17	0.01
KL44-09	866.5	869.5	0.0174	174	0.01	0.1	28	12	0.01	6	0.01	1	0.01	1.3	28	0.01
KL44-09	869.5	872.5	0.043	430	0.01	0.1	57	13	2	8	0.01	2	0.01	1.7	17	0.01
KL44-09	872.5	875.5	0.512	5120	0.19	1.8	460	15	3	6	0.01	19	0.01	4.5	26	0.01
KL44-09	875.5	878.5	1.3	13000	0.39	3.1	262	9	4	29	1	19	0.2	8.5	26	0.01
KL44-09	878.5	881.5	0.336	3360	0.11	1.3	271	11	6	8	1	10	0.6	2.8	46	0.01
KL44-09	881.5	884.5	0.511	5110	0.17	3.5	460	9	0.01	3	2	21	0.01	5.0	58	0.01
KL44-09	884.5	887.5	0.61	6100	0.31	2.2	305	10	3	3	1	15	0.01	3.5	38	0.01
KL44-09	887.5	890.5	0.84	8400	0.53	1.8	200	6	2	8	1	18	0.01	5.0	44	0.01
KL44-09	890.5	893.5	0.462	4620	0.2	0.8	81	6	0.01	27	1	14	0.2	3.9	45	0.01
KL44-09	893.5	896.5	0.056	560	0.02	0.1	30	7	2	9	0.01	3	0.2	1.9	35	0.01
KL44-09	896.5	899.2	0.169	1690	0.03	0.8	51	8	1	21	7	6	0.3	2.8	73	0.01
KL44-09	899.2	901	0.11	1100	0.02	0.1	49	14	1	158	1	5	0.2	2.7	152	0.01
KL44-09	901	904	0.77	7700	0.43	0.6	70	7	13	10	0.01	15	0.3	4.4	20	0.01
KL44-09	904	906.8	0.21	2100	0.42	0.1	33	6	8	25	1	7	0.2	7.3	33	0.01
KL44-09	906.8	909.3	0.151	1510	0.04	1.3	208	74	8	30	1	6	3.7	2.5	27	0.01
KL44-09	909.3	911.5	0.11	1100	0.05	13.4	326	1100	38	105	1	7	130	3.0	211	0.12
KL44-09	911.5	914.5	0.156	1560	0.02	1	71	31	3	54	1	4	0.5	5.8	46	0.01
KL44-09	914.5	917.5	0.49	4900	0.16	0.9	16	7	6	420	0.01	25	0.01	5.8	46	0.01
KL44-09	917.5	920.5	0.112	1120	0.01	0.7	35	12	1	61	1	4	0.2	2.3	126	0.01
KL44-09	920.5	923.6	0.094	940	0.01	0.6	31	13	2	116	1	5	0.01	2.5	126	0.01
KL44-09	923.6	926.5	0.066	660	0.01	0.1	39	9	12	59	1	4	0.2	4.4	227	0.01
KL44-09	926.5	929.5	0.197	1970	0.02	1	185	53	30	72	1	6	11.8	4.0	110	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL44-10	187.2	191															
KL44-10	191	194															
KL44-10	194	197															
KL44-10	206	208.5															
KL44-10	208.5	211.7															
KL44-10	237.16	240.2															
KL44-10	288	293															
KL44-10	293	295.7	0.0021		21	0.01	0.7	299	75	12	15	6	1	1.1	1.1	23	0.01
KL44-10	295.7	299	0.0036		36	0.01	1.7	315	146	15	69	10	1	1.5	2.8	20	0.01
KL44-10	299	302	0.0019		19	0.01	1.5	182	116	7	11	6	1	0.6	1.5	12	0.01
KL44-10	302	305	0.0022		22	0.01	4.9	1360	1100	11	5	6	1	4	22.2	14	0.34
KL44-10	305	307.9	0.0043		43	0.01	0.8	680	143	13	13	6	1	1.3	3.0	13	0.01
KL44-10	307.9	310.7	0.001		10	0.01	0.5	212	121	4	44	2	2	0.4	1.5	12	0.01
KL44-10	310.7	313.8	0.0048		48	0.01	0.7	680	500	10	25	3	1	0.7	2.8	10	0.01
KL44-10	313.8	316.9	0.0061		61	0.01	0.6	620	241	16	26	2	1	0.7	2.4	13	0.01
KL44-10	316.9	320.6	0.0014		14	0.01	0.5	720	317	13	8	1	3	1.3	3.8	16	0.12
KL44-10	320.6	323	0.0014		14	0.02	1.1	290	240	14	19	0.01	2	1.6	2.5	14	0.01
KL44-10	323	326	0.0072		72	0.02	0.9	600	215	15	11	3	2	1.6	1.5	10	0.01
KL44-10	326	329	0.0011		11	0.01	0.6	401	198	11	6	0.01	1	1.4	1.5	8	0.01
KL44-10	329	332	0.0013		13	0.01	0.7	409	392	5	10	0.01	1	0.5	4.5	9	0.01
KL44-10	332	335	0.0216		216	0.18	23.9	14500	28200	58	7	28	1	25	270.0	16	0.01
KL44-10	335	338	0.0197		197	0.25	3.8	3950	1590	78	38	14	2	7.8	19.0	22	0.23
KL44-10	338	341	0.035		350	2.45	4.4	16800	1720	570	48	4	3	44	14.8	47	2.94
KL44-10	341	344	0.0193		193	2.16	3.6	5260	1030	110	8	3	3	20	7.3	23	0.96
KL44-10	344	347	0.0066		66	0.34	2.5	2630	700	51	4	2	1	5.2	5.8	16	0.46
KL44-10	347	350	0.0045		45	0.3	1.5	2040	710	42	6	2	1	3.8	3.8	14	0.31
KL44-10	350	353	0.0061		61	0.28	4.8	3500	1530	43	14	15	1	5	13.1	12	0.49
KL44-10	353	356	0.0014		14	0.06	0.1	1000	140	16	11	3	1	1.6	3.3	12	0.11
KL44-10	356	359	0.0038		38	0.04	0.8	1120	550	7	8	1	1	3.2	3.0	12	0.13
KL44-10	359	362	0.0044		44	0.03	0.8	1370	740	18	4	1	1	4	5.3	11	0.22
KL44-10	362	365	0.004		40	0.06	1.1	1440	540	23	3	1	1	4.7	3.8	13	0.24
KL44-10	365	368	0.0056		56	1.59	2.2	2800	990	220	3	1	1	21	9.0	16	0.92
KL44-10	368	371	0.0025		25	0.2	0.8	930	337	31	5	2	1	3.3	4.8	11	0.2
KL44-10	371	374	0.0065		65	0.09	0.7	1040	354	19	28	1	3	3.9	6.0	18	0.13
KL44-10	374	377	0.0014		14	0.03	0.1	410	183	20	11	0.01	1	1.6	5.4	10	0.01
KL44-10	377	380	0.0203		203	0.04	0.6	750	398	32	10	1	3	3.3	4.5	22	0.13
KL44-10	380	383	0.0032		32	0.01	0.5	810	272	12	11	1	1	1.8	3.8	6	0.01
KL44-10	383	386	0.0022		22	0.01	0.7	590	480	10	17	3	2	1	4.5	11	0.01
KL44-10	386	389	0.0156		156	0.08	0.8	1320	1040	100	339	6	1	7.8	12.2	26	0.41
KL44-10	389	392	0.106		1060	0.16	1.4	2140	70	34	62	8	6	1.5	8.3	23	0.01
KL44-10	392	395	0.48		4800	0.37	3.4	21400	890	310	11	6	62	14	28.5	36	0.29
KL44-10	395	398	0.048		480	0.12	0.7	1810	73	110	105	8	13	3.1	3.5	55	0.01
KL44-10	398	401	0.0028		28	0.16	0.5	980	339	33	940	1	3	3.9	2.3	78	0.11
KL44-10	401	404	0.253		2530	0.15	3.1	83	82	13	148	4	5	5.2	4.8	36	0.01
KL44-10	404	407	0.0076		76	0.02	0.1	393	163	22	490	3	1	1.7	4.9	18	0.01
KL44-10	407	410	0.0365		365	0.05	0.8	430	186	43	167	1	3	2.5	5.3	82	0.01
KL44-10	410	413	0.103		1030	0.08	1	286	52	14	365	1	7	0.8	3.3	23	0.01
KL44-10	413	416	0.109		1090	0.13	1.2	780	22	13	29	0.01	3	0.4	2.3	20	0.01
KL44-10	416	419	0.5		5000	0.67	5.4	840	16	15	9	5	29	0.7	13.7	48	0.01
KL44-10	419	422	0.242		2420	0.98	3.1	650	44	16	61	7	14	1	14.4	19	0.01
KL44-10	422	425	0.72		7200	1.28	8.9	1520	25	13	36	5	20	0.7	6.8	18	0.01
KL44-10	425	428	0.204		2040	0.22	1.6	370	21	17	14	1	5	0.9	2.4	23	0.01
KL44-10	428	431	0.161		1610	0.22	1.9	166	39	7	364	1	5	0.8	2.5	27	0.01
KL44-10	431	434	0.35		3500	0.44	3.1	357	54	8	99	1	4	0.9	4.3	27	0.01
KL44-10	434	437	0.526		5260	0.89	4	930	92	16	5	2	9	0.8	9.8	53	0.01
KL44-10	437	440	0.24		2400	0.18	1.6	310	128	15	7	2	4	1.4	4.8	33	0.01
KL44-10	440	443	0.23		2300	0.19	1.8	236	57	15	13	4	17	1	9.3	21	0.01
KL44-10	443	446.8	0.475		4750	0.34	2.9	590	25	10	340	1	14	0.5	7.3	32	0.01
KL44-10	446.8	448.1	0.408		4080	0.26	100	370	45	20	709	1	11	1.1	5.0	70	0.01
KL44-10	448.1	450.8	0.24		2400	0.18	1.8	660	110	49	17	3	5	3.1	5.8	35	0.11
KL44-10	450.8	453.9	0.59		5900	0.52	2.7	670	190	200	43	2	12	28	7.3	40	0.24
KL44-10	453.9	457	0.528		5280	0.41	1	210	72	28	22	1	8	6.3	10.8	21	0.01
KL44-10	457	460	0.052		520	0.05	0.8	1000	680	23	284	0.01	5	4.8	4.0	34	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL44-10	460	462.5	1.54	15400	0.93	2.4	330	78	22	9	0.01	17	3.9	15.5	29	0.01
KL44-10	462.5	464	0.134	1340	0.11	2.3	27900	218	42	10	11	81	2.9	27.0	32	0.01
KL44-10	464	467	0.1	1000	0.06	3.5	2810	930	40	7	12	7	2.1	9.5	39	0.01
KL44-10	467	470	0.102	1020	0.15	2.2	510	301	61	1370	14	3	1.2	29.0	89	0.01
KL44-10	470	473	0.78	7800	0.99	3.6	690	169	28	235	4	20	3.6	23.5	35	0.01
KL44-10	473	476	0.93	9300	0.36	6.7	870	148	75	5	1	20	6.8	18.3	30	0.01
KL44-10	476	479	0.305	3050	0.21	3.4	730	261	40	5	2	9	3.8	12.0	46	0.01
KL44-10	479	482	0.33	3300	0.18	3.9	393	240	51	6	2	12	10.4	10.0	20	0.01
KL44-10	482	485	0.56	5600	0.33	6.1	460	110	42	2	1	23	2.5	9.0	27	0.01
KL44-10	485	488	0.149	1490	0.12	2	218	190	23	24	1	7	2.5	5.3	30	0.01
KL44-10	488	491	0.128	1280	0.17	3.2	9930	261	27	4	10	4	1	13.3	28	0.01
KL44-10	491	494	0.058	580	0.09	1.5	1250	122	21	4	3	3	1.1	5.0	33	0.01
KL44-10	494	497	0.9	9000	0.53	9.4	22400	162	41	3	70	4	2.2	116.0	95	0.01
KL44-10	497	500	1.9	19000	1.74	18	8160	163	34	13	56	25	1.8	56.0	47	0.01
KL44-10	500	503	2.2	22000	2.02	12.5	258	74	36	3	38	24	0.4	46.5	55	0.01
KL44-10	503	506	1.69	16900	1.34	8.5	162	32	19	2	38	14	0.7	43.0	90	0.01
KL44-10	506	509	1	10000	0.88	4.9	81	20	11	2	26	18	0.9	31.5	90	0.01
KL44-10	509	512	1.76	17600	1.61	8.3	275	91	14	5	8	14	2.6	22.0	66	0.01
KL44-10	512	514.2	1.55	15500	1.51	7.5	371	135	21	10	28	30	2.2	42.0	27	0.01
KL44-10	514.2	516.8	2.68	26800	1.44	9.3	113	29	11	4	21	28	0.8	33.6	32	0.01
KL44-10	516.8	519.5	1.42	14200	1.36	8.5	298	205	9	5	16	24	3.1	34.0	39	0.01
KL44-10	519.5	523.1	2.89	28900	1.33	9.5	540	48	5	8	34	25	1.5	15.5	68	0.01
KL44-10	523.1	526.2	4.25	42500	1.3	20.2	1730	580	41	4	5	30	16	36.3	84	0.3
KL44-10	526.2	527	4.08	40800	1.4	10.4	710	16	18	5	5	53	1	33.8	51	0.01
KL44-10	527	530	3.01	30100	1.4	20.3	810	15	19	1	15	97	0.5	41.3	43	0.01
KL44-10	530	531.3	3.69	36900	0.68	31	162	19	4	36	5	19	0.8	40.0	217	0.01
KL44-10	531.3	532.7	0.83	8300	0.55	14.3	500	820	32	22	4	14	40	17.0	57	0.01
KL44-10	532.7	534.2	0.59	5900	0.24	5.9	137	64	12	193	5	17	6.3	11.5	96	0.01
KL44-10	534.2	537	1.54	15400	0.64	9.6	55	31	39	40	36	15	1.8	36.0	98	0.01
KL44-10	537	540	1.13	11300	0.38	3.7	96	52	66	71	5	18	3.2	42.0	156	0.01
KL44-10	540	543	0.83	8300	0.32	4.2	470	190	65	47	6	18	4.4	32.0	110	0.01
KL44-10	543	544	0.66	6600	0.2	2.7	286	123	28	18	7	8	3.9	14.5	79	0.01
KL44-10	544	546.2	0.79	7900	0.24	12.8	1050	620	83	27	3	8	24	14.5	92	0.17
KL44-10	546.2	547.8	0.77	7700	0.43	24.3	3430	3500	130	8	5	12	28	23.2	128	0.44
KL44-10	547.8	550.4	0.521	5210	0.43	8.1	1160	540	100	10	43	11	14	10.5	59	0.14
KL44-10	550.4	552.8	0.432	4320	0.34	5	152	66	25	38	22	10	5	11.7	175	0.01
KL44-10	552.8	556.3	0.55	5500	0.56	6.6	52	25	9	4	17	11	1.3	7.8	88	0.01
KL44-10	556.3	559.3	0.66	6600	0.54	5.7	62	30	14	6	16	13	1.8	13.7	150	0.01
KL44-10	559.3	563	1.02	10200	0.32	12.3	156	105	50	4	19	11	9.9	17.5	101	0.01
KL44-10	563	566	0.61	6100	0.33	6.2	56	32	20	6	8	12	2.1	10.8	105	0.01
KL44-10	566	569	0.55	5500	0.44	6.6	92	55	20	42	26	10	1.9	11.5	97	0.01
KL44-10	569	572														
KL44-10	572	575	0.524	5240	0.37	4.8	2100	32	24	10	8	11	1	12.8	99	0.01
KL44-10	575	578	0.33	3300	0.36	3.1	124	62	38	6	14	13	3.7	14.0	112	0.01
KL44-10	578	581	0.396	3960	0.34	8.5	960	750	28	10	26	9	4.1	9.5	80	0.01
KL44-10	581	584	0.31	3100	0.16	2.9	123	88	13	4	16	10	1.3	10.0	101	0.01
KL44-10	584	587	0.237	2370	0.2	1.5	61	33	14	8	21	9	1.4	8.0	86	0.01
KL44-10	587	590	0.22	2200	0.15	1.1	157	158	5	4	3	8	0.7	7.5	86	0.01
KL44-10	590	593	0.21	2100	0.07	1.1	97	38	5	40	3	8	0.8	5.9	77	0.01
KL44-10	593	596	0.64	6400	0.4	18.7	1880	2090	23	8	7	13	4.6	9.5	81	0.13
KL44-10	596	598.1	0.442	4420	0.13	1.9	120	92	5	6	5	11	0.6	12.8	78	0.01
KL44-10	598.1	601.2	0.215	2150	0.11	3.7	2370	1880	12	7	3	9	2.1	6.3	69	0.14
KL44-10	601.2	604.3	0.182	1820	0.12	5	870	590	19	6	16	7	1.9	6.0	94	0.01
KL44-10	604.3	607.4	0.225	2250	0.19	6.8	190	235	32	4	16	10	15.7	11.0	79	0.01
KL44-10	607.4	610.5	0.225	2250	0.19	6.4	182	265	16	12	8	11	4	6.9	74	0.01
KL44-10	610.5	613.6	0.396	3960	0.28	2.8	126	33	14	7	2	13	1.6	6.3	107	0.01
KL44-10	613.6	616.7	1.12	11200	0.68	17.5	173	54	19	6	214	13	9	13.5	85	0.4
KL44-10	616.7	619.8	0.71	7100	3.67	4.2	2370	137	5	8	7	11	1.2	5.8	67	0.67
KL44-10	619.8	623.4	1.05	10500	0.5	5.4	64	24	54	4	6	10	20	16.5	69	0.2
KL44-10	623.4	626	0.73	7300	0.23	5.3	235	98	36	3	11	5	30	14.8	191	0.25
KL44-10	626	629	0.24	2400	0.15	2.3	106	88	29	13	6	7	10.3	12.8	36	0.12
KL44-10	629	632	0.183	1830	0.16	1.8	292	80	26	35	5	6	8.3	7.5	44	0.16
KL44-10	632	635	0.065	650	0.09	2.2	116	56	24	175	4	7	3.1	5.8	231	0.13

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL44-10	635	638	0.204	2040	0.15	3.1	121	68	14	13	6	4	3.8	4.3	243	0.16
KL44-10	638	641	0.69	6900	0.28	3.6	64	50	8	9	5	5	2.6	3.8	224	0.01
KL44-10	641	644	0.496	4960	0.29	2.6	192	81	17	8	3	6	4.8	5.5	183	0.01
KL44-10	644	647	0.28	2800	0.1	2	198	72	12	24	3	6	3.2	5.4	234	0.18
KL44-10	647	650	0.388	3880	0.3	2.1	135	69	14	54	4	10	1.9	10.0	40	0.1
KL44-10	650	652.5	0.147	1470	0.11	1.3	139	62	8	77	2	4	2.2	4.0	229	0.1
KL44-10	652.5	655.6	0.115	1150	0.07	1	132	58	6	68	2	5	1.5	4.5	200	0.1
KL44-10	655.6	657.3	0.372	3720	0.11	7.3	372	175	12	43	21	5	5.4	3.3	228	0.17
KL44-10	657.3	660	0.085	850	0.08	2.2	331	335	8	293	5	7	3.3	8.8	215	0.01
KL44-10	660	662.5	0.24	2400	0.12	3.6	112	64	11	103	3	6	8.6	3.8	185	0.11
KL44-10	662.5	664.4	0.325	3250	0.16	5.4	123	91	76	105	5	3	11.4	3.3	226	0.24
KL44-10	664.4	668	0.275	2750	0.15	3.6	200	117	10	105	7	5	5.6	4.0	180	0.12
KL44-10	668	670	0.23	2300	0.19	1.4	187	53	23	870	6	7	1	9.7	34	0.01
KL44-10	670	673.4	0.24	2400	0.1	2.2	227	138	4	41	2	5	4.4	4.4	120	0.01
KL44-10	673.4	676.3	0.165	1650	0.08	2.1	50	68	18	53	3	8	8.4	6.3	229	0.01
KL44-10	676.3	679.4	0.31	3100	0.1	1.9	217	166	4	33	2	5	5.2	5.5	238	0.14
KL44-10	679.4	682.6	0.176	1760	0.09	3.6	940	430	6	35	3	5	5.8	6.5	204	0.16
KL44-10	682.6	684	0.145	1450	0.26	7.7	4530	1380	16	64	13	15	17.6	10.5	131	0.53
KL44-10	684	687	0.75	7500	0.54	18.7	1200	530	47	24	22	6	17.3	7.9	265	0.68
KL44-10	687	689.6	0.503	5030	3.23	26.1	500	850	55	41	26	7	48	7.2	111	0.61
KL44-10	689.6	692.6	0.124	1240	0.15	4.1	410	275	16	30	6	6	16	9.0	128	0.18
KL44-10	692.6	695	0.065	650	0.04	1.9	108	112	12	18	4	7	13.3	5.8	190	0.01
KL44-10	695	698	0.084	840	0.07	1.8	173	102	7	35	1	4	4.1	3.1	177	0.01
KL44-10	729	733.6														
KL44-10	733.6	824														
KL46-01	0	3	0.0028	28	0.01	0.1	32	12	6	2	0.01	1	0.8	1.2	30	0.01
KL46-01	3	6	0.0168	168	0.3	1.7	349	221	28	5	1	2	3.9	16.3	41	0.54
KL46-01	6	9	0.0009	9	0.01	0.1	39	19	7	3	0.01	1	0.6	1.4	18	0.01
KL46-01	9	12	0.003	30	0.06	0.1	75	60	11	4	2	1	0.4	1.0	23	0.01
KL46-01	12	15	0.017	170	0.01	0.7	450	90	15	1	4	2	0.9	2.0	12	0.01
KL46-01	15	18	0.0012	12	0.01	0.1	98	21	17	3	1	1	1.2	1.5	20	0.01
KL46-01	18	21	0.002	20	0.12	0.1	98	38	17	3	0.01	1	0.8	1.6	17	0.01
KL46-01	21	23.1	0.001	10	0.06	0.1	32	18	14	2	0.01	1	1.1	1.7	13	0.12
KL46-01	23.1	26.2	0.0005	5	0.01	0.1	28	13	8	1	0.01	1	0.6	1.1	18	0.01
KL46-01	26.2	29.3	0.0005	5	0.01	0.1	36	12	7	1	0.01	1	0.3	1.0	18	0.01
KL46-01	29.3	32.4	0.0025	25	0.01	0.1	25	13	6	1	0.01	1	0.5	1.7	23	0.01
KL46-01	32.4	35.5	0.001	10	0.01	0.1	44	13	7	1	0.01	1	0.4	0.7	20	0.01
KL46-01	35.5	37.2	0.0009	9	0.01	0.1	69	22	16	1	0.01	2	0.6	2.2	23	0.01
KL46-01	37.2	39	0.0068	68	0.01	0.1	65	18	11	1	0.01	1	0.4	1.1	22	0.01
KL46-01	39	42	0.0051	51	0.05	0.5	135	93	79	12	2	3	3.3	6.2	89	0.01
KL46-01	42	44.2	0.0013	13	0.03	0.1	68	32	20	3	0.01	2	0.7	2.3	23	0.01
KL46-01	44.2	46.1	0.0012	12	0.01	0.1	75	21	10	2	0.01	1	0.4	1.2	24	0.01
KL46-01	46.1	48	0.0009	9	0.01	0.1	56	20	10	1	0.01	1	0.6	1.2	25	0.01
KL46-01	48	51	0.0024	24	0.02	0.1	52	25	10	2	0.01	1	0.6	1.3	22	0.01
KL46-01	51	54	0.0008	8	0.01	0.1	34	24	5	1	0.01	1	2.1	1.9	18	0.01
KL46-01	54	57	0.0009	9	0.01	0.1	345	30	7	2	0.01	1	0.9	0.9	20	0.01
KL46-01	57	60	0.0008	8	0.01	0.1	49	35	7	2	0.01	1	0.6	1.4	25	0.01
KL46-01	60	63	0.0036	36	0.17	0.1	70	42	11	4	0.01	1	1	2.1	22	0.1
KL46-01	63	66	0.0008	8	0.01	0.1	80	19	7	2	0.01	1	0.5	1.2	26	0.01
KL46-01	66	69	0.0007	7	0.01	0.1	75	16	7	2	0.01	1	0.3	1.5	24	0.01
KL46-01	69	72	0.0013	13	0.01	0.1	46	14	9	3	0.01	1	0.5	2.5	27	0.01
KL46-01	72	75	0.0175	175	0.06	0.1	107	38	54	25	7	1	4.3	3.1	50	0.01
KL46-01	75	78	0.0011	11	0.01	0.1	50	18	9	3	0.01	1	0.6	1.9	40	0.01
KL46-01	78	81	0.0027	27	0.01	0.1	161	11	6	2	0.01	2	0.5	2.1	31	0.01
KL46-01	81	84	0.0026	26	0.07	0.1	216	20	11	3	1	2	1	1.8	33	0.01
KL46-01	84	86.4	0.0158	158	0.03	0.1	49	26	49	12	6	1	2.7	1.9	40	0.01
KL46-01	86.4	89.2	0.0012	12	0.01	0.1	55	70	7	4	2	2	0.3	2.0	38	0.01
KL46-01	89.2	92.2	0.0006	6	0.01	0.1	30	21	14	1	0.01	1	0.3	1.9	27	0.01
KL46-01	92.2	95.3	0.0011	11	0.01	0.5	139	131	14	1	1	1	1.1	4.0	78	0.01
KL46-01	95.3	96.9	0.331	3310	0.21	1.5	151	30	740	49	6	3	16.5	7.2	189	0.46
KL46-01	96.9	98.4	0.026	260	0.04	0.8	90	69	130	39	12	4	4.4	3.3	61	0.01
KL46-01	98.4	101.4	0.0059	59	0.05	0.9	289	530	160	22	3	3	4.7	15.7	81	0.01
KL46-01	101.4	103.2	0.0301	301	0.22	1.1	500	281	220	61	8	4	9.3	12.2	78	0.11

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL46-01	103.2	105.5	0.0038		38	0.17	0.8	128	27	120	3	1	9	52	22.5	39	2.49
KL46-01	105.5	106.4	0.059		590	0.54	8.4	2760	2360	380	28	6	10	371	74.0	65	13.1
KL46-01	106.4	108.7	0.0213		213	0.39	4.9	1020	920	260	23	9	6	52	28.8	122	1.93
KL46-01	108.7	111	0.068		680	0.31	5.1	1760	510	360	41	19	5	38	18.0	255	1.52
KL46-01	111	114	0.255		2550	0.43	5.8	470	250	860	62	76	9	34	13.3	161	1.9
KL46-01	114	117	0.0027		27	0.27	0.6	151	58	150	22	1	3	3.8	1.8	81	0.31
KL46-01	117	120	0.003		30	0.25	0.1	105	26	120	8	1	3	2.3	1.3	71	0.27
KL46-01	120	123	0.0029		29	0.24	0.1	68	16	82	18	1	2	1.6	1.2	81	0.19
KL46-01	123	126	0.128		1280	0.34	2.5	110	70	450	57	66	4	7.7	5.5	81	0.61
KL46-01	126	128.1	0.079		790	0.14	1.1	77	30	320	20	18	3	7.4	3.2	70	0.46
KL46-01	128.1	130	0.168		1680	0.17	2.5	315	71	300	18	52	1	8.6	4.1	49	0.42
KL46-01	130	132	0.432		4320	0.22	7.6	238	67	830	63	56	3	43	8.8	38	1.48
KL46-01	132	135	0.0034		34	0.01	0.1	30	16	8	3	0.01	1	0.4	0.9	18	0.01
KL46-01	135	138	0.336		3360	0.19	2.9	147	90	290	90	110	4	22	8.3	57	0.11
KL46-01	138	141	0.314		3140	0.56	4.1	316	172	1040	381	110	9	42	14.7	141	0.18
KL46-01	141	144	0.0276		276	0.24	1	440	138	250	136	16	4	13.6	3.0	68	0.11
KL46-01	144	147	0.052		520	0.25	1.4	770	194	330	68	12	5	15.1	5.3	66	0.15
KL46-01	147	150.2	0.0172		172	1	3.4	215	136	420	282	38	6	24	7.7	140	0.37
KL46-01	150.2	152	0.0174		174	0.11	1.3	215	79	52	28	12	1	8.8	4.6	31	0.13
KL46-01	152	153.8	0.0084		84	0.17	2	840	354	47	11	10	1	19	4.8	38	0.1
KL46-01	153.8	155.8	0.0181		181	0.24	13.2	2000	2610	100	33	30	4	20	20.5	37	0.18
KL46-01	155.8	158.4	0.003		30	0.28	1.2	213	143	64	17	2	1	10.8	2.7	30	0.12
KL46-01	158.4	161.4	0.0051		51	0.08	0.7	235	136	26	12	2	2	22	2.2	18	0.01
KL46-01	161.4	164.6	0.0018		18	0.03	0.1	170	32	8	4	1	1	3.9	0.7	22	0.01
KL46-01	164.6	166.8	0.0017		17	0.02	0.1	185	43	10	4	0.01	1	2.9	0.8	20	0.01
KL46-01	166.8	168	0.0018		18	0.04	0.1	172	30	14	5	1	1	2.8	0.7	22	0.01
KL46-01	168	171	0.0013		13	0.07	0.1	290	146	21	6	1	1	3.9	1.6	23	0.01
KL46-01	171	173.8	0.0011		11	0.13	0.5	89	79	32	6	4	1	4.1	1.3	20	0.01
KL46-01	173.8	175.4	0.0005		5	0.03	0.1	21	21	9	3	0.01	1	1.2	0.8	19	0.01
KL46-01	175.4	177	0.0032		32	0.08	0.1	90	98	15	4	1	1	2.8	1.6	23	0.01
KL46-01	177	180	0.0016		16	0.08	0.1	327	257	10	4	0.01	1	2.3	2.1	23	0.01
KL46-01	180	182.6	0.0015		15	0.25	0.1	149	89	56	5	1	1	4.7	1.2	22	0.1
KL46-01	182.6	185.7	0.0025		25	1.14	1	306	104	110	13	5	1	8.8	2.9	32	0.26
KL46-01	185.7	187.9	0.0008		8	0.22	0.1	46	46	32	6	2	1	1.9	1.3	19	0.01
KL46-01	187.9	189.9	0.0006		6	0.06	0.1	38	37	12	3	1	1	0.8	0.6	22	0.01
KL46-01	189.9	192	0.0004		4	0.04	0.1	23	25	8	3	1	1	0.4	0.5	23	0.01
KL46-01	192	194.6	0.001		10	0.12	0.1	136	80	20	5	2	1	0.8	1.3	23	0.01
KL46-01	194.6	197.6	0.0008		8	0.06	0.1	71	89	13	6	2	1	0.6	2.6	24	0.01
KL46-01	197.6	200	0.0045		45	0.12	2.3	430	870	32	19	11	4	1.6	8.6	28	0.01
KL46-01	200	203.2	0.0122		122	0.04	1.3	840	520	31	21	6	3	1.2	4.9	15	0.01
KL46-01	203.2	204.5	0.0012		12	0.06	0.7	124	124	19	5	3	1	0.7	2.2	19	0.01
KL46-01	204.5	206.5	0.0024		24	0.11	1.2	104	100	130	6	2	1	3.9	1.8	25	0.12
KL46-01	206.5	209.6	0.0039		39	0.16	0.8	440	274	39	15	2	1	2.1	3.6	73	0.2
KL46-01	209.6	212.6	0.003		30	0.04	0.9	440	349	12	6	3	1	0.5	2.7	34	0.01
KL46-01	212.6	215	0.0017		17	0.04	0.5	103	140	14	7	2	1	1.6	1.5	27	0.01
KL46-01	215	217.7	0.0033		33	0.1	3.6	345	820	24	10	14	1	0.7	7.0	31	0.01
KL46-01	217.7	218.9	0.0037		37	0.05	0.6	197	154	15	23	2	2	0.8	1.8	23	0.01
KL46-01	218.9	221.3	0.0043		43	0.11	0.5	103	113	10	4	1	2	3.1	2.2	26	0.01
KL46-01	221.3	224.4	0.0035		35	0.05	1.8	1470	1020	7	9	7	3	1.1	5.4	12	0.01
KL46-01	224.4	227.5	0.056		560	0.06	3.2	3890	1530	74	20	16	3	2.5	10.8	27	0.1
KL46-01	227.5	230.5	0.0073		73	0.01	1	460	226	17	18	6	2	1.1	2.8	11	0.01
KL46-01	230.5	232.8	0.0012		12	0.01	0.1	27	14	13	4	0.01	3	0.4	0.8	20	0.01
KL46-01	232.8	235.4	0.0204		204	0.06	3.5	2100	860	31	20	20	2	1.2	6.2	26	0.01
KL46-01	235.4	238.4	0.01		100	0.02	3.9	1720	750	22	24	22	2	0.9	7.5	18	0.01
KL46-01	238.4	241.5	0.0082		82	0.01	0.1	69	190	77	2	1	3	2.1	7.6	33	0.1
KL46-01	241.5	243	0.003		30	0.01	1.1	470	172	12	9	12	3	0.8	3.1	14	0.01
KL46-01	243	245.8	0.0073		73	0.02	2	550	329	24	12	53	1	1.6	6.0	12	0.01
KL46-01	245.8	247.8	0.0024		24	0.03	0.6	296	170	25	6	4	1	0.7	1.9	12	0.01
KL46-01	247.8	250.9	0.007		70	0.01	1.9	500	238	12	11	39	1	0.7	2.5	12	0.01
KL46-01	250.9	254	0.0049		49	0.01	0.9	1450	590	8	7	4	1	0.6	3.3	14	0.01
KL46-01	254	257.1	0.0174		174	0.04	1.4	394	384	70	13	19	4	7.2	8.3	17	0.01
KL46-01	257.1	260.2	0.24		2400	0.41	45	10500	8000	760	130	147	1	130	72.0	22	0.16
KL46-01	260.2	263.3	0.0075		75	0.04	1.9	1700	610	19	8	14	1	2.7	6.4	17	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL46-01	263.3	265.4	0.5	5000	0.28	12.6	1710	1080	1450	33	31	1	160	13.3	18	0.3
KL46-01	265.4	267.4	0.0026	26	0.03	0.1	238	65	18	4	1	1	1.3	2.4	15	0.01
KL46-01	267.4	268.7	0.0042	42	0.01	0.1	530	51	9	3	2	1	0.6	1.5	16	0.01
KL46-01	268.7	271.3	0.0076	76	0.06	0.1	830	192	51	4	2	1	2.3	3.4	11	0.01
KL46-01	271.3	273	0.0367	367	0.18	0.1	580	88	120	4	1	3	3.5	2.5	21	0.35
KL46-01	273	276	0.0125	125	0.18	1.3	2200	790	190	7	0.01	2	7.8	6.6	15	0.1
KL46-01	276	279	0.0266	266	0.07	0.5	460	110	110	8	1	6	2.8	5.1	16	0.01
KL46-01	279	282	0.0087	87	0.16	0.7	5400	760	150	10	1	3	13.1	5.3	16	0.12
KL46-01	282	285	0.198	1980	0.25	2.6	31600	2700	890	6	1	6	110	7.1	15	0.39
KL46-01	285	288	0.0082	82	0.18	1.7	9280	2300	130	3	1	3	12.6	3.6	16	0.19
KL46-01	288	291	0.0401	401	0.22	1.5	4050	790	230	34	10	5	11.7	15.9	25	0.18
KL46-01	291	294	0.046	460	0.09	0.8	930	134	90	21	6	4	3.5	7.0	21	0.1
KL46-01	294	297	0.0152	152	0.24	0.9	820	182	81	4	5	3	4.5	3.5	18	0.17
KL46-01	297	300	0.027	270	1.85	2.1	5440	287	260	5	8	10	13.6	9.5	32	0.73
KL46-01	300	303	0.0293	293	0.25	1.1	1590	229	110	6	18	5	10.2	6.1	21	0.35
KL46-01	303	306	0.0079	79	0.22	1.2	2600	950	65	7	3	3	4.2	3.5	24	0.14
KL46-01	306	309	0.052	520	0.27	3.7	7540	1560	120	9	44	1	7.2	29.2	20	0.54
KL46-01	309	312	0.0181	181	0.24	1.3	4120	610	86	6	28	2	5	6.1	25	0.43
KL46-01	312	315	0.0047	47	0.17	0.6	870	239	39	2	1	2	2.3	1.6	21	0.26
KL46-01	315	318	0.0115	115	0.17	0.1	1560	112	87	3	1	3	3.3	2.7	17	0.41
KL46-01	318	321	0.0072	72	0.53	1.4	2860	700	500	3	6	1	14	8.5	15	0.22
KL46-01	321	324	0.0347	347	0.54	0.8	1920	121	180	6	29	6	7.2	5.1	26	1.08
KL46-01	324	327	0.0056	56	0.07	0.1	670	132	34	5	1	1	1.3	0.6	18	0.01
KL46-01	327	328.2	0.0103	103	0.04	0.1	1260	193	20	2	1	1	1.5	0.0	18	0.01
KL46-01	328.2	329.5	0.093	930	0.11	0.7	510	52	51	220	8	7	2	5.0	58	0.01
KL46-01	329.5	332.6	0.34	3400	0.44	1.4	209	22	33	12	18	10	1.6	3.2	43	0.01
KL46-01	332.6	335.7	0.123	1230	0.27	1.2	6210	166	180	9	29	14	4.9	10.0	55	0.23
KL46-01	335.7	337.2	0.21	2100	0.09	0.9	2600	53	30	3	1	14	1	5.0	14	0.01
KL46-01	337.2	338.8	0.33	3300	0.13	1.7	270	26	35	13	3	16	1.6	4.1	36	0.01
KL46-01	338.8	341.9	0.119	1190	0.14	1.6	10800	44	38	4	21	12	3.3	7.7	31	0.01
KL46-01	341.9	345	0.3	3000	0.34	2.4	204	119	83	75	26	10	3	12.0	56	0.01
KL46-01	345	348	0.129	1290	0.09	1.3	800	176	33	54	8	8	1.4	12.9	30	0.01
KL46-01	348	351	0.103	1030	0.08	1.5	242	132	32	780	34	14	1.7	49.0	56	0.01
KL46-01	351	354	0.072	720	0.2	1.3	700	306	110	113	40	17	3	53.0	49	0.01
KL46-01	354	357	0.165	1650	0.3	1.3	1130	152	67	50	35	15	2.3	15.5	20	0.01
KL46-01	357	360	0.25	2500	0.23	1.7	14300	49	41	2	6	29	1.8	12.7	21	0.01
KL46-01	360	363	0.0089	89	0.06	0.1	480	44	35	1	1	2	1.7	0.6	17	0.01
KL46-01	363	366	0.73	7300	0.94	6.1	970	87	44	4	14	11	1.9	5.0	17	0.01
KL46-01	366	369	0.47	4700	0.34	4.4	3040	42	31	24	14	18	1.6	5.2	21	0.01
KL46-01	369	372	0.33	3300	0.24	1.4	252	31	21	25	3	15	2.9	2.9	15	0.01
KL46-01	372	375	0.39	3900	0.16	2.2	178	25	32	39	7	22	1.5	5.6	21	0.01
KL46-01	375	378	0.58	5800	0.32	3.1	660	47	180	21	33	22	4.7	13.2	28	0.27
KL46-01	378	381	0.62	6200	0.23	2.7	282	18	19	17	3	27	1.4	5.6	15	0.01
KL46-01	381	384	0.71	7100	0.37	1.9	530	46	270	7	6	19	2.9	7.4	53	0.11
KL46-01	384	387	0.313	3130	0.31	2.9	2930	244	140	10	35	17	6.1	11.7	64	0.19
KL46-01	387	390	0.67	6700	0.29	4.2	1370	121	95	9	4	31	3.2	6.6	45	0.01
KL46-01	390	393	0.171	1710	0.08	1.2	500	49	56	19	5	14	7.1	3.3	39	0.01
KL46-01	393	396	0.184	1840	0.11	1	205	31	39	6	7	12	2.3	3.8	24	0.01
KL46-01	396	399	0.495	4950	0.2	2.2	223	33	38	5	4	14	2.5	5.2	17	0.01
KL46-01	399	402	0.62	6200	0.73	2.7	176	21	35	23	14	18	2.4	5.8	36	0.01
KL46-01	402	405	0.0128	128	0.21	0.1	760	58	52	3	1	1	1.7	1.2	17	0.28
KL46-01	405	408	0.132	1320	0.11	0.5	195	26	43	14	1	8	1.1	2.5	22	0.01
KL46-01	408	410.9	0.275	2750	0.21	1.3	98	57	7	15	11	6	0.6	11.8	13	0.01
KL46-01	410.9	413.9	0.24	2400	0.14	0.5	59	17	9	50	2	8	0.4	2.7	15	0.01
KL46-01	413.9	415.6	0.052	520	0.02	0.1	26	12	4	13	3	3	0.3	1.1	9	0.01
KL46-01	415.6	418.6	0.138	1380	0.04	0.8	46	17	3	169	5	6	0.3	4.7	12	0.01
KL46-01	418.6	420	0.178	1780	0.11	1.3	88	40	21	300	7	10	1.1	8.3	13	0.01
KL46-01	420	423	0.061	610	0.08	0.5	68	26	12	363	3	7	0.8	3.0	29	0.01
KL46-01	423	426	0.131	1310	0.27	0.9	5600	1200	150	980	8	16	2.8	3.4	43	0.11
KL46-01	426	429	0.13	1300	0.13	0.8	126	36	24	890	12	13	0.4	6.1	84	0.01
KL46-01	429	432	0.67	6700	0.36	2.9	700	81	360	22	22	23	1.8	5.8	44	0.01
KL46-01	432	435	0.62	6200	0.24	1.8	399	23	30	11	2	19	0.6	5.5	32	0.01
KL46-01	435	438	0.52	5200	0.16	1.6	760	104	93	16	1	19	1.2	6.2	106	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL46-01	438	440.2	0.55	5500	1.01	3.3	3820	1200	840	127	4	14	11.7	5.8	77	0.12
KL46-01	440.2	442.9	0.42	4200	0.31	1.6	169	38	54	94	2	12	2.1	6.5	31	0.01
KL46-01	442.9	444	0.112	1120	0.44	1	970	180	97	196	1	8	2.6	3.3	43	0.12
KL46-01	444	447	0.0249	249	0.05	0.1	152	20	23	37	2	5	0.4	1.5	24	0.01
KL46-01	447	450	0.0148	148	0.02	0.1	66	11	21	64	0.01	5	0.4	0.0	52	0.01
KL46-01	450	453	0.78	7800	0.15	1.8	204	9	50	13	1	30	2.6	5.8	58	0.01
KL46-01	453	455	1.02	10200	0.2	1.3	154	21	46	195	1	22	1.7	7.5	38	0.01
KL46-01	455	458	0.27	2700	0.16	1.3	163	54	34	27	1	12	0.8	4.3	67	0.01
KL46-01	458	459.9	0.059	590	0.4	0.6	287	128	100	30	0.01	12	1.3	2.7	32	0.01
KL46-01	459.9	462	0.112	1120	5.22	1.4	157	68	250	75	2	10	3.4	4.3	37	0.78
KL46-01	462	465	0.0186	186	0.28	0.1	215	80	67	660	1	8	2.6	2.0	29	0.01
KL46-01	465	468	0.27	2700	0.21	3	303	156	32	9	20	6	4.6	2.5	19	0.01
KL46-01	468	471	0.08	800	0.09	0.1	265	68	69	15	1	10	2.5	1.8	44	0.01
KL46-01	471	473.1	0.075	750	0.07	0.1	320	66	120	80	1	6	3.2	2.0	54	0.01
KL46-01	473.1	475	0.26	2600	0.13	1.5	408	61	200	42	1	4	3.1	4.8	20	0.01
KL46-01	475	477.4	0.22	2200	0.11	1.3	480	47	250	17	0.01	9	2.4	4.3	46	0.01
KL46-01	477.4	480	0.0082	82	0.01	0.1	168	8	15	4	0.01	10	0.3	0.0	14	0.01
KL46-01	480	483	0.028	280	0.02	0.1	274	36	28	14	1	11	0.7	0.8	20	0.01
KL46-01	483	486	0.32	3200	0.16	2.6	650	500	160	203	3	10	5.4	8.3	54	0.12
KL46-01	486	489	0.0257	257	0.01	0.1	130	15	12	9	1	7	0.4	0.5	15	0.01
KL46-01	489	492	0.062	620	0.02	0.1	388	112	32	5	0.01	9	0.7	0.8	16	0.01
KL46-01	492	495	0.85	8500	0.67	4.2	500	48	40	11	20	13	1.3	10.5	19	0.01
KL46-01	495	498	0.097	970	0.14	0.8	930	134	61	7	1	9	2.2	2.0	18	0.01
KL46-01	498	499.9	0.0346	346	0.06	0.1	374	30	22	4	0.01	8	0.6	0.6	15	0.01
KL46-01	499.9	501.3	0.066	660	0.06	0.1	318	25	64	5	0.01	4	0.7	1.3	17	0.01
KL46-01	501.3	504	0.18	1800	0.22	0.9	650	188	370	6	1	10	4.9	3.2	34	0.29
KL46-01	504	507	0.064	640	0.05	0.5	396	42	150	7	0.01	5	1.5	1.5	30	0.01
KL46-01	507	511.8	0.1	1000	0.06	0.1	1130	125	120	30	2	5	1.3	2.3	16	0.01
KL46-01	511.8	512.8	0.055	550	0.17	0.6	2020	580	100	52	3	4	1.7	1.5	28	0.1
KL46-01	512.8	515.7	0.37	3700	0.69	1.9	1410	265	300	9	2	9	3.9	5.5	21	0.23
KL46-01	515.7	517.8	0.16	1600	0.22	0.9	940	87	200	8	2	3	1.1	4.6	16	0.01
KL46-01	517.8	519	0.117	1170	0.3	0.5	1290	117	250	5	2	4	1.7	3.8	22	0.1
KL46-01	519	522	0.0304	304	0.22	0.1	1610	113	180	6	0.01	3	1	3.0	13	0.15
KL46-01	522	525	0.0388	388	0.4	1.5	4500	940	260	11	2	3	2.3	4.8	12	0.28
KL46-01	525	528	0.55	5500	0.4	3.5	4300	800	460	12	18	6	2.3	13.6	13	0.22
KL46-01	528	529.9	0.167	1670	0.3	1.3	1180	95	76	8	9	2	0.4	4.8	11	0.01
KL46-01	529.9	532.9	0.98	9800	0.52	4.3	1190	192	250	7	13	2	1.4	10.9	36	0.01
KL46-01	532.9	536	1.8	18000	0.75	3.6	1190	302	300	10	2	10	2.5	23.0	65	0.01
KL46-01	536	539	2.6	26000	1.08	5.9	1920	490	330	6	4	21	1.8	62.5	84	0.01
KL46-01	539	542.2	1.67	16700	1.17	2.1	450	53	7	10	2	18	1.7	14.5	49	0.01
KL46-01	542.2	545.3	2.48	24800	1.56	3.7	490	48	12	54	3	41	1.9	13.0	62	0.01
KL46-01	545.3	548.4	3	30000	1.3	5.1	700	35	3	43	3	28	1.6	15.0	34	0.01
KL46-01	548.4	551.5	3.95	39500	2.52	7.4	980	36	1	43	8	23	1.2	3.0	35	0.01
KL46-01	551.5	554.6	3.72	37200	3.14	4.8	1130	121	2	23	4	18	1.5	12.5	43	0.01
KL46-01	554.6	557.7	3.18	31800	5.18	14.1	2040	93	5	20	48	23	1.4	20.0	48	0.01
KL46-01	557.7	559.3	2.7	27000	1.96	10.6	291	18	4	4370	5	15	1.5	17.5	91	0.01
KL46-01	559.3	560.8	1.71	17100	11.2	7.6	2150	800	20	930	5	14	0.6	13.0	78	0.01
KL46-01	560.8	563.9	0.68	6800	1.59	1.8	1090	450	23	296	4	9	0.4	15.5	67	0.01
KL46-01	563.9	567	1.2	12000	1.32	15.3	690	105	41	99	40	14	0.6	17.5	86	0.01
KL46-01	567	570	1.67	16700	2.98	10.7	4200	1440	35	250	6	23	1	56.0	105	0.01
KL46-01	570	573	0.7	7000	2.72	11.2	4600	930	59	16	18	28	8	32.0	155	0.01
KL46-01	573	576	1.06	10600	1.16	5.1	720	92	39	62	6	16	0.6	12.2	132	0.01
KL46-01	576	579	0.96	9600	0.89	6.7	3300	870	36	117	6	16	0.4	14.0	98	0.44
KL46-01	579	582	0.67	6700	0.53	27.1	110	28	31	45	5	13	0.4	4.0	87	0.01
KL46-01	582	585	0.93	9300	0.99	20.1	550	104	70	60	7	12	0.5	11.0	113	0.01
KL46-01	585	588	0.85	8500	1.07	21.2	530	62	33	134	9	12	0.4	7.7	78	0.01
KL46-01	588	591	0.69	6900	1.87	12	2300	690	39	38	7	12	0.4	12.5	87	0.01
KL46-01	591	594	0.6	6000	1.6	18.9	278	102	31	75	7	14	0.2	12.0	105	0.01
KL46-01	594	597	0.45	4500	0.4	9.8	349	205	23	253	6	16	0.3	15.5	88	0.01
KL46-01	597	600	0.77	7700	0.39	12.1	660	150	36	146	7	14	0.5	13.0	95	0.01
KL46-01	600	603	0.79	7900	0.4	7.7	128	40	27	322	4	15	0.3	15.8	82	0.01
KL46-01	603	606	0.69	6900	0.3	14.7	264	184	28	218	8	13	0.7	11.3	80	0.01
KL46-01	606	609	0.72	7200	0.44	6.1	166	65	18	175	4	19	0.4	6.0	90	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL46-01	609	612	1.22	12200	0.37	24.8	211	56	23	430	5	21	1	13.5	95	0.01
KL46-01	612	615	0.73	7300	0.27	5.3	54	18	41	219	5	15	0.2	15.8	110	0.01
KL46-01	615	618	0.78	7800	0.28	2.9	254	70	17	328	8	20	0.4	23.2	109	0.01
KL46-01	618	621	1.01	10100	0.21	3.1	91	201	9	144	6	16	0.4	24.8	112	0.01
KL46-01	621	624	0.86	8600	0.28	1.9	92	40	10	133	6	17	0.7	20.3	82	0.01
KL46-01	624	627	0.96	9600	0.53	2.2	109	22	14	138	6	16	0.9	23.5	93	0.01
KL46-01	627	630	0.74	7400	0.65	3.6	101	40	25	45	9	15	1.3	17.0	99	0.01
KL46-01	630	633	0.61	6100	0.75	7.8	152	43	55	82	10	11	0.2	13.0	98	0.01
KL46-01	633	636	0.67	6700	1.18	5.4	420	113	36	218	8	9	0.2	14.5	103	0.01
KL46-01	636	639	0.91	9100	0.79	4.8	1520	670	630	242	6	16	0.8	27.8	126	0.32
KL46-01	639	642	0.66	6600	0.32	3.3	91	25	65	64	5	13	7.4	19.8	57	0.01
KL46-01	642	645	0.76	7600	0.36	3.3	101	32	34	179	5	14	0.01	16.8	127	0.01
KL46-01	645	648	0.75	7500	0.49	3	48	13	14	110	4	15	0.8	17.5	88	0.01
KL46-01	648	651	0.96	9600	0.25	2.4	167	83	31	840	4	26	0.9	27.5	104	0.01
KL46-01	651	654	0.85	8500	0.36	3.2	62	15	35	72	5	22	0.8	23.5	43	0.01
KL46-01	654	657	0.61	6100	0.28	2.5	182	104	38	335	4	36	0.4	21.0	90	0.01
KL46-01	657	660	0.63	6300	0.25	3.6	53	37	22	161	3	16	0.01	8.0	76	0.01
KL46-01	660	663	1.33	13300	0.25	3.9	154	48	33	269	10	28	1.2	22.0	37	0.01
KL46-01	663	666	0.94	9400	0.27	3.6	175	166	110	227	5	16	1.9	23.0	82	0.1
KL46-01	666	669	0.85	8500	0.33	2.3	82	17	29	400	5	26	0.3	15.7	79	0.01
KL46-01	669	672	0.52	5200	0.44	2	78	25	37	450	5	27	0.3	12.5	67	0.01
KL46-01	672	675	0.36	3600	0.28	1.8	168	95	15	165	5	26	0.01	15.0	84	0.13
KL46-01	675	678	0.27	2700	0.27	1.3	127	38	16	400	4	22	0.01	11.5	63	0.21
KL46-01	678	681	0.28	2800	0.23	1.2	40	25	19	610	4	13	0.01	10.8	62	0.01
KL46-01	681	684	0.46	4600	0.35	2.8	60	18	8	750	3	20	0.01	10.0	54	0.01
KL46-01	684	687	0.58	5800	0.31	3.8	162	20	4	352	1	21	0.01	8.1	62	0.01
KL46-01	687	690	0.94	9400	0.48	4	355	85	11	620	1	19	0.01	6.5	63	0.37
KL46-01	690	693	0.67	6700	0.36	2.6	185	129	9	860	1	23	0.01	8.4	55	0.62
KL46-01	693	696	0.59	5900	0.49	2	690	179	13	200	2	30	0.3	15.8	88	3.27
KL46-01	696	699	0.68	6800	1.16	4.2	910	208	50	500	4	47	2.1	11.8	85	3.25
KL46-01	699	701.3	0.54	5400	1.21	3.4	970	187	9	369	3	83	0.4	17.0	36	3.7
KL46-01	701.3	704.3	0.54	5400	1.25	4.3	750	349	18	380	7	35	0.7	14.8	40	4.71
KL46-01	704.3	705.7	0.202	2020	2.49	3.7	157	386	4	400	2	20	0.01	6.0	62	5.03
KL46-01	705.7	708	0.82	8200	1.04	4.9	177	280	40	196	6	42	0.6	15.5	55	3.85
KL46-01	708	711	0.83	8300	4.47	6.1	1700	680	1850	1060	3	49	24.8	16.3	118	7.06
KL46-01	711	714	0.3	3000	0.27	1.8	950	313	790	460	3	35	14.6	13.8	93	2.4
KL46-01	714	717	0.199	1990	0.27	1.5	1040	304	320	680	5	72	8.2	38.0	102	2.14
KL46-01	717	720	0.059	590	0.16	1.5	440	293	92	690	3	47	2.9	31.0	100	0.45
KL46-01	720	722.2	0.059	590	0.13	2	530	410	120	500	2	37	3.7	15.5	127	0.55
KL46-01	722.2	725.3	0.069	690	0.1	0.6	116	240	160	378	2	25	5.5	12.8	127	0.5
KL46-01	725.3	728.3	0.183	1830	0.2	2.1	194	336	390	112	5	20	11	14.0	166	1
KL46-01	728.3	731.4	0.033	330	0.07	0.1	59	34	62	186	2	7	1.5	7.3	88	0.19
KL46-01	731.4	734.5	0.14	1400	0.13	0.8	119	112	220	127	4	9	2.3	7.6	146	0.64
KL46-01	734.5	737.6	0.187	1870	0.13	1.1	147	158	230	132	4	7	1.4	8.1	194	0.86
KL46-01	737.6	740.7	0.54	5400	0.24	2.2	1800	660	1130	86	5	7	14.5	9.0	81	3.81
KL46-01	740.7	743.7	0.9	9000	1.3	4.8	1540	1030	550	387	4	25	3	10.0	101	3.2
KL46-01	743.7	746.8	0.38	3800	0.24	2	126	50	120	400	3	18	1.5	5.8	65	0.32
KL46-01	746.8	749.9	0.27	2700	0.14	1.6	57	23	5	235	2	14	0.4	4.0	68	0.01
KL46-01	749.9	753	0.52	5200	0.23	1.7	47	14	4	950	2	17	0.2	5.3	55	0.01
KL46-01	753	756	0.21	2100	0.12	1.4	74	235	7	1160	1	10	0.7	4.1	19	0.01
KL46-01	756	759	1.38	13800	0.82	4	75	10	4	660	2	59	0.3	6.0	38	0.01
KL46-01	759	762	0.498	4980	0.23	2.3	85	31	6	450	2	35	0.5	4.3	23	0.01
KL46-01	762	765	0.267	2670	0.1	1.2	26	12	4	394	1	11	0.5	2.0	10	0.01
KL46-01	765	768	0.229	2290	0.05	1.4	97	86	5	740	2	10	0.5	5.0	11	0.01
KL46-01	768	771	0.406	4060	0.17	1.3	38	10	5	278	1	19	0.4	2.8	23	0.01
KL46-01	771	773.8	0.93	9300	0.79	1.8	56	9	21	9	0.01	36	1.2	9.0	33	0.01
KL46-01	773.8	776.9	0.71	7100	0.55	1.5	75	13	5	4	0.01	36	0.4	6.5	47	0.01
KL46-01	776.9	780	0.365	3650	0.4	1.2	80	7	4	7	0.01	28	0.5	4.3	25	0.01
KL46-01	780	783	0.467	4670	0.33	2.7	124	8	15	3	6	21	1.4	4.5	24	0.01
KL46-01	783	786	0.485	4850	0.38	1.7	131	19	12	9	3	22	1	3.8	29	0.01
KL46-01	786	789	0.51	5100	0.5	2.5	203	56	49	7	4	16	2.4	5.5	33	0.01
KL46-01	789	792	0.309	3090	0.41	1.3	116	15	22	7	2	10	1.9	2.3	24	0.01
KL46-01	792	795	0.516	5160	0.55	1.7	109	15	22	22	2	7	1.1	7.5	22	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL46-01	795	798	0.195	1950	0.26	1.5	199	23	10	2	2	6	0.5	1.8	14	0.01
KL46-01	798	801	0.94	9400	1.17	5.5	203	14	21	4	2	17	3	6.5	25	0.01
KL46-01	801	804	0.047	470	0.07	0.1	127	35	8	3	1	1	0.2	1.2	11	0.01
KL46-01	804	806.4	0.128	1280	0.18	1.8	143	50	6	4	1	5	0.01	2.0	9	0.01
KL46-01	806.4	809.5	0.0264	264	0.01	0.7	110	56	2	56	1	1	0.01	1.1	8	0.01
KL46-01	809.5	811.3	0.059	590	0.03	0.1	44	11	4	4	2	1	0.01	1.0	10	0.01
KL46-01	811.3	814.1	0.0154	154	0.01	0.1	96	16	3	6	3	1	0.01	1.1	8	0.01
KL46-01	814.1	816	0.023	230	0.01	0.5	14	8	2	7	2	1	0.01	0.8	8	0.01
KL46-01	816	818.6	0.0105	105	0.01	0.1	37	11	3	6	1	2	0.01	1.3	12	0.01
KL46-01	818.6	820	0.061	610	0.03	0.9	1380	11	5	33	4	3	0.01	10.2	22	0.01
KL46-01	820	822	0.04	400	0.04	0.1	90	12	8	11	4	8	0.7	2.5	32	0.01
KL46-01	822	824.2	0.011	110	0.01	0.1	68	44	3	3	5	1	0.2	1.3	12	0.01
KL46-01	824.2	826.9	0.0312	312	0.03	0.1	22	11	6	10	28	1	0.3	1.5	18	0.01
KL46-01	826.9	828	0.092	920	0.04	0.5	63	26	17	20	4	1	0.2	3.5	16	0.01
KL46-01	828	829.5	0.0305	305	0.02	0.6	129	34	9	11	6	1	0.01	2.3	12	0.01
KL46-01	829.5	831	0.0258	258	0.01	0.5	133	74	2	4	2	1	0.2	1.3	13	0.01
KL46-01	831	834	0.14	1400	0.06	1.7	228	125	26	4	7	2	0.3	3.0	13	0.01
KL46-01	834	837	0.049	490	0.04	0.5	80	34	3	12	7	2	0.01	2.5	17	0.01
KL46-01	837	839.8	0.0115	115	0.02	0.5	24	14	2	5	5	1	0.01	1.3	17	0.01
KL46-01	839.8	842.9	0.0147	147	0.01	0.1	25	9	1	3	1	1	0.01	0.8	9	0.01
KL46-01	842.9	844.3	0.0168	168	0.03	0.1	50	24	2	4	2	1	0.01	1.3	13	0.01
KL46-01	844.3	846	0.0103	103	0.01	0.6	32	11	2	6	3	1	0.01	0.5	19	0.01
KL46-01	846	847.5	0.102	1020	0.04	0.1	103	10	8	4	2	1	0.2	2.8	18	0.01
KL46-01	847.5	849.3	0.1	1000	0.02	0.6	48	12	6	3	6	1	0.3	8.2	18	0.01
KL46-01	849.3	852	0.043	430	0.02	0.6	56	22	3	6	3	1	0.01	1.2	11	0.01
KL46-01	852	855	0.106	1060	0.04	0.6	132	22	6	6	4	3	0.01	2.0	18	0.01
KL46-01	855	857.4	0.11	1100	0.06	0.8	261	30	5	29	1	3	0.8	1.3	20	0.01
KL46-01	857.4	860.5	0.452	4520	0.25	2	234	10	19	5	0.01	22	0.3	4.8	21	0.01
KL46-01	860.5	863.6	0.396	3960	0.43	3.2	380	7	16	37	1	24	7.9	5.4	30	0.01
KL46-01	863.6	866.7	0.52	5200	0.36	2.6	332	11	9	25	0.01	13	0.6	6.5	21	0.01
KL46-01	866.7	869.8	0.71	7100	0.55	3.4	223	27	13	61	1	24	1	7.4	29	0.01
KL46-01	869.8	872.2	0.401	4010	0.15	1.3	148	35	9	760	0.01	11	0.5	4.0	15	0.01
KL46-01	872.2	873.6	0.509	5090	0.2	1.8	139	23	12	25	2	16	0.6	6.0	20	0.01
KL46-01	873.6	876	0.74	7400	0.29	2.3	120	11	7	500	1	18	1.1	7.0	16	0.01
KL46-01	876	879	0.71	7100	0.49	1.9	214	21	9	14	1	31	0.2	5.0	20	0.01
KL46-01	879	882	1.07	10700	0.91	3	266	43	21	20	1	23	0.3	7.0	18	0.01
KL46-01	882	885	0.338	3380	0.19	1.1	66	20	25	83	0.01	9	0.3	1.6	15	0.01
KL46-01	885	888	0.101	1010	0.06	0.8	107	20	7	14	0.01	4	0.2	2.1	11	0.01
KL46-01	888	891	0.095	950	0.05	0.8	21	6	3	192	0.01	5	0.2	1.7	33	0.01
KL46-01	891	894	0.6	6000	0.29	2.5	193	41	12	221	2	16	0.7	5.5	26	0.01
KL46-01	894	897	0.74	7400	0.55	3.3	281	9	8	117	1	23	0.4	6.8	29	0.01
KL46-01	897	900	0.06	600	0.06	0.1	144	9	8	12	0.01	4	0.3	1.6	28	0.01
KL46-01	900	903	0.077	770	0.12	0.8	70	7	6	28	1	5	0.2	1.8	24	0.01
KL46-01	903	906	0.079	790	0.08	0.7	104	15	5	15	0.01	8	0.01	1.7	26	0.01
KL46-01	906	908.6	0.042	420	0.03	0.5	73	11	6	5	0.01	4	0.01	1.8	17	0.01
KL46-01	908.6	911.7	0.307	3070	0.21	1.5	194	8	5	17	0.01	15	0.3	7.9	25	0.01
KL46-01	911.7	914.8	0.37	3700	0.26	2	180	7	3	18	0.01	9	0.2	4.5	26	0.01
KL46-01	914.8	917.9	0.64	6400	0.59	2	259	76	7	22	1	24	0.3	7.0	32	0.01
KL46-01	917.9	921	0.36	3600	0.11	0.7	58	8	1	16	0.01	32	0.2	7.5	27	0.01
KL46-01	921	924	0.52	5200	0.37	2.4	180	10	4	18	0.01	35	0.2	12.4	41	0.01
KL46-01	924	927	0.469	4690	0.4	2	168	30	5	41	0.01	17	0.2	2.8	43	0.26
KL46-01	927	930	0.66	6600	0.39	2.2	172	43	5	8	2	23	0.2	7.3	41	0.01
KL46-01	930	933	0.471	4710	0.31	1.6	93	28	5	28	0.01	14	0.01	5.0	30	0.01
KL46-01	933	936	1.09	10900	0.45	2.6	172	22	29	95	0.01	27	0.6	8.0	40	0.01
KL46-01	936	939	0.22	2200	0.07	1.9	89	59	21	281	0.01	8	0.8	2.3	25	0.01
KL46-01	939	942	0.126	1260	0.06	1.5	140	291	22	155	1	5	1.1	2.4	75	0.01
KL46-01	942	945	0.285	2850	0.53	1.1	209	81	26	142	3	6	0.9	4.0	73	0.01
KL46-01	945	948	1.65	16500	15.6	11.8	274	56	12	8	269	14	3	16.9	30	0.23
KL46-01	948	951	0.257	2570	0.36	1.1	70	29	38	25	5	4	1.1	3.4	16	0.01
KL46-02	0	2.5	0.0246	246	0.12	0.1	237	68	7	7	0.01	1	0.7	0.5	26	0.01
KL46-02	2.5	4.6	0.002	20	0.01	0.1	32	9	10	2	0.01	1	0.3	1.3	37	0.28
KL46-02	4.6	7.7	0.0037	37	0.01	0.1	32	10	16	4	0.01	1	0.4	1.3	24	0.01
KL46-02	7.7	10.8	0.0018	18	0.01	0.1	24	9	14	2	0.01	1	0.3	0.8	15	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL46-02	10.8	13.9	0.0033		33	0.01	0.1	89	8	22	3	0.01	1	0.4	1.7	13	0.01
KL46-02	13.9	15.9	0.0036		36	0.01	0.1	32	10	30	4	0.01	1	0.8	1.6	27	0.13
KL46-02	15.9	18.8	0.0021		21	0.01	0.1	43	14	23	7	0.01	1	1.1	1.6	25	0.1
KL46-02	18.8	21.5	0.0053		53	0.03	0.1	46	22	38	9	1	1	1.4	1.6	20	0.01
KL46-02	21.5	24	0.0037		37	0.01	0.1	22	15	10	3	0.01	1	0.7	1.4	17	0.01
KL46-02	24	26	0.0012		12	0.01	0.1	26	14	17	3	0.01	1	0.6	1.6	18	0.01
KL46-02	26	29.1	0.0024		24	0.01	0.1	16	11	14	3	0.01	1	0.3	0.9	19	0.01
KL46-02	29.1	32.1	0.0013		13	0.01	0.1	18	8	12	4	0.01	1	0.3	1.6	22	0.01
KL46-02	32.1	35.3	0.0011		11	0.01	0.1	24	9	16	3	0.01	1	0.5	1.6	24	0.01
KL46-02	35.3	38.5	0.0012		12	0.09	0.1	26	11	22	4	0.01	1	0.6	0.5	24	0.15
KL46-02	38.5	41.5	0.0013		13	0.01	0.1	20	9	8	3	0.01	1	0.2	0.0	20	0.01
KL46-02	41.5	44.5	0.0016		16	0.01	0.1	23	10	14	4	0.01	1	0.01	1.1	22	0.01
KL46-02	44.5	47.5	0.0012		12	0.03	0.1	34	9	9	3	0.01	1	0.2	2.4	22	0.01
KL46-02	47.5	50.5	0.0011		11	0.01	0.1	19	12	14	6	0.01	1	0.3	1.3	30	0.01
KL46-02	50.5	53.5	0.0008		8	0.01	0.1	21	11	10	2	0.01	2	0.4	1.2	28	0.01
KL46-02	53.5	56.5	0.0053		53	0.02	0.1	39	15	17	2	0.01	1	0.6	1.5	22	0.01
KL46-02	56.5	59.2	0.0029		29	0.04	0.1	49	13	12	2	0.01	1	0.7	2.0	21	0.01
KL46-02	59.2	62.3	0.0027		27	0.01	0.1	25	31	11	8	0.01	1	0.8	3.0	28	0.01
KL46-02	62.3	65.4	0.0062		62	0.02	0.1	22	10	8	7	0.01	1	0.4	1.1	28	0.01
KL46-02	65.4	68.4	0.0012		12	0.01	0.1	17	11	10	2	0.01	1	0.4	1.6	21	0.01
KL46-02	68.4	71.5	0.0021		21	0.03	0.1	29	20	22	8	1	1	1.1	2.3	39	0.01
KL46-02	71.5	74.5	0.001		10	0.01	0.1	24	12	9	2	0.01	1	0.3	1.1	28	0.01
KL46-02	74.5	77.5	0.0012		12	0.02	0.1	62	16	18	3	0.01	1	0.6	2.5	27	0.01
KL46-02	77.5	80.5	0.0024		24	0.01	0.1	40	17	19	1	0.01	1	1	1.7	25	0.01
KL46-02	80.5	83.5	0.0045		45	0.02	0.1	83	41	26	8	0.01	1	1.9	2.2	41	0.01
KL46-02	83.5	86.5	0.0039		39	0.02	0.1	144	122	37	3	0.01	1	1.6	2.3	42	0.01
KL46-02	86.5	89.5	0.0124		124	0.11	0.1	96	96	110	16	0.01	1	2.2	5.4	36	0.01
KL46-02	89.5	92.5	0.0017		17	0.04	0.1	70	99	33	5	0.01	1	1.5	5.5	110	0.01
KL46-02	92.5	95.7	0.0064		64	0.26	4	750	760	63	3	1	1	7.9	36.0	41	0.01
KL46-02	95.7	97.8	0.38		3800	1.53	72	62500	41600	1210	164	670	9	150	1360.0	95	1.6
KL46-02	97.8	100.9	2.34		23400	2.68	88	4200	2900	5600	405	2900	26	420	98.0	97	4.61
KL46-02	100.9	104.5	0.181		1810	1.78	9.5	378	160	710	103	102	8	156	23.3	176	1.69
KL46-02	104.5	107.5	0.172		1720	1.94	8.3	830	570	940	720	106	12	66	60.0	111	3.45
KL46-02	107.5	110.5	0.0172		172	0.32	1.1	94	62	140	24	92	6	7.5	9.5	193	0.43
KL46-02	110.5	113.4	0.005		50	0.19	0.6	134	81	76	41	7	1	3.8	2.1	153	0.22
KL46-02	113.4	116.4	0.0199		199	1.12	1.1	300	99	380	1070	192	1	20	17.8	54	1.98
KL46-02	116.4	119.5	0.0032		32	0.46	0.5	94	24	180	53	107	3	5	4.9	132	0.52
KL46-02	119.5	122.3	0.0035		35	1.5	1.6	362	114	440	290	22	7	9.3	7.3	122	1.14
KL46-02	122.3	125.5	0.0059		59	1.12	1.6	267	86	490	480	56	7	12.2	5.3	161	1.05
KL46-02	125.5	128	0.009		90	1.05	1.4	244	329	410	910	40	12	11.2	6.7	68	0.79
KL46-02	128	131	0.0132		132	1.6	1.9	480	270	640	590	18	10	20	6.8	135	1.76
KL46-02	131	134	0.0038		38	1.41	0.7	275	64	460	194	6	6	14	7.3	59	1.79
KL46-02	134	136	0.0195		195	1.36	1	235	78	760	318	20	8	19.5	6.2	58	1.77
KL46-02	136	139.7	0.034		340	1.49	1.3	550	238	1260	590	34	9	21	6.5	116	1.97
KL46-02	139.7	147.6	0.0381		381	1.47	3.1	750	240	740	258	27	9	25	8.7	181	1.6
KL46-02	147.6	149.5	0.0202		202	0.07	0.6	70	26	49	51	4	1	2.9	1.1	25	0.1
KL46-02	149.5	151.9	0.0081		81	0.08	0.8	339	65	49	38	6	1	6.4	2.6	25	0.1
KL46-02	151.9	155.5	0.0079		79	0.13	1.7	373	139	85	16	4	1	6.3	4.5	17	0.16
KL46-02	155.5	158.5	0.0043		43	0.02	0.5	160	46	24	11	3	1	2.2	2.8	17	0.01
KL46-02	158.5	161.5	0.0193		193	0.06	1.3	510	54	85	10	4	1	9.6	2.7	20	0.15
KL46-02	161.5	164.5	0.0157		157	0.08	0.9	148	43	69	20	4	1	5.2	1.3	27	0.2
KL46-02	164.5	167.7	0.0159		159	0.09	1	167	62	84	18	10	1	5.2	1.4	24	0.1
KL46-02	167.7	170.5	0.094		940	0.52	5.7	1370	236	540	47	20	1	24	6.2	31	0.27
KL46-02	170.5	173.2	0.23		2300	0.32	7.1	950	355	700	176	120	17	23	17.8	27	0.16
KL46-02	173.2	175.3	0.118		1180	0.75	3.8	1010	179	480	164	42	8	20	8.3	31	0.25
KL46-02	175.3	178.7	0.0336		336	0.2	1.4	760	164	78	83	20	1	3.6	4.3	21	0.1
KL46-02	178.7	182.5	0.63		6300	0.59	5.3	7200	55	1050	156	38	8	25	11.0	38	0.45
KL46-02	182.5	185.4	0.65		6500	0.33	5.3	5100	60	1250	140	17	8	40	12.0	38	0.52
KL46-02	185.4	187.7	0.105		1050	0.1	1.1	1140	49	270	44	3	4	7	4.0	22	0.14
KL46-02	187.7	190.9	0.097		970	0.09	2.4	1780	188	200	128	22	3	7.9	6.1	25	0.1
KL46-02	190.9	194.5	0.129		1290	0.27	12	20500	4700	300	285	12	3	20	32.0	33	0.75
KL46-02	194.5	197.5	0.0185		185	0.05	2.3	510	93	60	57	4	1	4	2.8	39	0.01
KL46-02	197.5	199.9	0.018		180	0.03	0.9	244	65	40	18	3	1	2.4	1.6	28	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL46-02	199.9	202.9	0.065		650	0.08	1.5	159	37	210	32	1	1	9.9	2.8	27	0.01
KL46-02	202.9	205.2	0.112		1120	0.13	1.7	347	89	170	27	2	1	12	2.2	26	0.15
KL46-02	205.2	206.9	0.048		480	0.19	2.1	2470	146	110	162	20	2	5.4	8.5	12	0.1
KL46-02	206.9	209.5	0.14		1400	0.18	3.1	1260	298	80	107	28	1	3.3	8.0	15	0.01
KL46-02	209.5	212.5	0.124		1240	0.24	2.9	3190	790	60	124	24	2	2.9	9.8	14	0.01
KL46-02	212.5	215.3	0.023		230	0.05	1.2	460	207	32	18	2	1	2.7	2.0	10	0.01
KL46-02	215.3	218	0.01		100	0.05	0.9	430	180	21	24	1	1	2.6	1.5	10	0.01
KL46-02	218	220.8	0.0113		113	0.1	2.8	1640	950	27	25	2	1	4.3	5.5	12	0.2
KL46-02	220.8	223.2	0.39		3900	0.09	8.8	7100	850	270	32	70	5	80	14.5	23	0.23
KL46-02	223.2	226.6	0.0264		264	0.05	1.9	1430	590	58	25	1	1	4.7	1.8	15	0.1
KL46-02	226.6	229.5	0.0183		183	0.01	0.9	362	117	18	28	2	1	2.4	1.5	13	0.01
KL46-02	229.5	231.6	0.024		240	0.04	2.1	710	257	36	14	1	1	5.6	2.1	12	0.01
KL46-02	231.6	233.5	0.0123		123	0.03	0.9	680	267	39	13	1	1	3.4	2.2	11	0.01
KL46-02	233.5	236.2	0.0095		95	0.07	0.9	540	136	35	28	1	1	3.6	1.8	15	0.01
KL46-02	236.2	238.7	0.0146		146	0.1	1.4	1230	247	43	17	1	1	5	1.0	13	0.01
KL46-02	238.7	241.8	0.092		920	0.25	7	9000	3000	160	21	3	1	31	4.5	13	0.17
KL46-02	241.8	244.5	0.056		560	0.15	12.4	6500	4300	210	13	1	1	70	2.8	10	0.19
KL46-02	244.5	247.5	0.134		1340	0.33	1.4	500	115	57	23	18	1	2.4	3.3	16	0.01
KL46-02	247.5	251.5	0.054		540	0.19	1.5	910	365	56	38	2	1	4.9	3.4	19	0.01
KL46-02	251.5	254.5	0.074		740	0.24	1	296	38	43	245	2	1	1.7	2.5	17	0.01
KL46-02	254.5	257.5	0.079		790	0.17	4.3	510	208	94	37	5	1	51	2.8	20	0.1
KL46-02	257.5	260.5	0.57		5700	1.07	9	1090	268	440	54	8	10	47	17.2	52	0.22
KL46-02	260.5	263.5	0.297		2970	0.4	10.2	3930	2480	330	23	13	4	40	8.0	34	0.36
KL46-02	263.5	266.5	0.72		7200	0.6	7	2300	690	490	54	14	13	10.5	11.5	61	0.43
KL46-02	266.5	269.5	0.65		6500	0.74	6.1	1030	177	290	37	2	28	9	7.8	44	0.13
KL46-02	269.5	272.5	0.2		2000	0.35	5.6	4250	1460	210	27	4	8	6.8	7.3	33	1.02
KL46-02	272.5	275.5	0.128		1280	0.21	1.5	1010	111	77	18	2	9	3.8	3.0	22	0.01
KL46-02	275.5	278.5	0.24		2400	0.88	2.3	460	43	180	24	24	20	3	6.0	20	0.01
KL46-02	278.5	281.5	0.339		3390	0.47	4.1	1650	56	120	35	3	21	4.3	3.8	23	0.01
KL46-02	281.5	284.5	0.22		2200	0.7	2.6	820	220	240	430	3	18	14.5	6.3	21	0.15
KL46-02	284.5	287.5	0.32		3200	0.71	4.3	1670	201	350	85	2	20	28	7.8	24	0.1
KL46-02	287.5	290.5	0.154		1540	0.44	2.3	29300	123	220	41	2	54	40	12.5	34	0.26
KL46-02	290.5	293.5	0.25		2500	1.36	43	13600	12100	1180	98	21	20	44	4.0	49	0.19
KL46-02	293.5	296.5	0.141		1410	0.44	7.9	2260	1950	200	234	0.01	6	11.4	1.5	60	0.11
KL46-02	296.5	299.5	0.265		2650	1.06	12.7	4120	2230	440	364	1	6	15.8	4.8	41	0.29
KL46-02	299.5	302.5	0.29		2900	0.56	6	720	333	210	650	1	7	8.7	4.5	100	0.2
KL46-02	302.5	305.5	0.072		720	0.15	1	207	48	120	260	0.01	6	4.8	2.0	55	0.01
KL46-02	305.5	307.5	0.21		2100	0.36	4.1	1890	600	200	56	2	10	9.2	4.5	86	0.31
KL46-02	307.5	310.5	0.098		980	0.14	2.1	420	133	51	296	1	7	2.9	1.9	50	0.01
KL46-02	310.5	313.5	0.124		1240	0.13	5.9	960	400	37	610	2	6	3.2	12.3	80	0.01
KL46-02	313.5	316.5	0.105		1050	0.11	1.5	650	236	40	550	3	7	2.2	2.2	41	0.01
KL46-02	316.5	319.5	0.098		980	0.12	1.5	630	233	31	1000	1	4	1.6	3.5	16	0.01
KL46-02	319.5	322.5	0.137		1370	0.23	1.1	630	183	39	520	1	5	1.3	3.0	17	0.01
KL46-02	322.5	325.5	0.376		3760	0.26	3.3	2110	540	66	1070	16	6	6	6.3	13	0.01
KL46-02	325.5	328.5	0.22		2200	0.15	2.2	346	219	39	1410	6	9	2.4	7.5	45	0.01
KL46-02	328.5	331.5	0.47		4700	0.23	4.6	600	325	53	860	8	9	4.1	7.3	47	0.01
KL46-02	331.5	334.3	0.6		6000	0.26	5.8	590	130	77	345	5	10	2.9	10.8	56	0.01
KL46-02	334.3	337.5	0.73		7300	0.4	2.9	600	328	120	125	1	13	5.7	6.5	68	0.11
KL46-02	337.5	340.5	2.11		21100	3.15	12.9	7100	840	800	63	4	56	60	15.2	45	0.48
KL46-02	340.5	343.5	2.13		21300	1.87	15.4	870	215	870	980	7	37	32	10.5	55	0.27
KL46-02	343.5	345.5	1.28		12800	2.08	8.5	314	136	450	520	3	17	14.5	2.0	39	0.28
KL46-02	345.5	347.5	0.413		4130	0.88	4.3	600	169	400	36	8	71	5.2	0.0	31	0.11
KL46-02	347.5	350.5	0.0172		172	0.25	3.2	1200	540	68	10	1	1	3.9	2.7	13	0.01
KL46-02	350.5	353.5	0.0049		49	0.37	1.4	830	480	390	5	1	1	4	1.9	12	0.1
KL46-02	353.5	356.5	0.0085		85	0.71	4	1990	1250	830	5	1	1	12.7	4.6	22	0.19
KL46-02	356.5	359.5	0.011		110	0.31	1.7	770	331	110	6	2	1	3.9	3.6	14	0.01
KL46-02	359.5	362.5	0.0094		94	0.22	1.4	510	213	67	12	1	2	4.4	3.7	16	0.01
KL46-02	362.5	365.5	0.0042		42	0.06	0.6	147	60	25	4	0.01	1	3.6	2.3	14	0.01
KL46-02	365.5	368.5	0.0041		41	0.07	1.2	183	94	21	2	0.01	1	2.2	2.7	13	0.01
KL46-02	368.5	371.5	0.0046		46	0.14	1.4	273	142	28	2	0.01	1	2	4.2	15	0.1
KL46-02	371.5	374.5	0.0124		124	0.15	1	560	158	46	8	0.01	2	2.5	3.8	16	0.01
KL46-02	374.5	377.5	0.0017		17	0.02	4.1	450	900	11	2	0.01	1	5	3.9	18	0.01
KL46-02	377.5	380.5	0.0023		23	0.05	0.7	660	171	19	2	0.01	1	3	5.8	22	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL46-02	380.5	383.5	0.0053		53	0.1	4	2930	1100	52	3	0.01	1	4.8	31.3	24	0.01
KL46-02	383.5	386.5	0.0072		72	0.02	0.1	123	72	9	3	0.01	1	0.5	1.5	20	0.01
KL46-02	386.5	389.5	0.0013		13	0.02	0.1	140	64	19	3	0.01	1	1	2.2	16	0.01
KL46-02	389.5	392.5	0.0009		9	0.01	0.1	88	34	6	3	0.01	1	0.3	1.0	15	0.01
KL46-02	392.5	395.5	0.0016		16	0.02	0.1	180	60	20	4	0.01	1	0.2	0.9	20	0.01
KL46-02	395.5	398.5	0.0032		32	0.05	0.1	254	84	20	4	0.01	1	0.8	2.3	16	0.01
KL46-02	398.5	401.5	0.0019		19	0.02	0.1	680	520	21	6	0.01	1	1.2	5.4	17	0.01
KL46-02	401.5	404.5	0.0019		19	0.02	0.1	500	221	41	5	0.01	1	1.6	4.9	21	0.01
KL46-02	404.5	407.5	0.0038		38	0.27	0.1	2370	1860	32	23	3	1	2.8	2.2	18	0.01
KL46-02	407.5	410.5	0.0027		27	0.03	0.7	184	233	26	3	3	1	0.8	3.8	27	0.01
KL46-02	410.5	413.5	0.0022		22	0.02	0.1	167	110	30	4	0.01	3	1.6	1.6	27	0.01
KL46-02	413.5	416.5	0.144		1440	0.09	0.1	375	22	43	5	0.01	11	1.5	1.4	30	0.01
KL46-02	416.5	419.5	0.0035		35	0.01	0.1	76	21	18	3	0.01	2	1	0.0	22	0.01
KL46-02	419.5	422.5	0.0056		56	0.03	0.1	75	18	22	7	0.01	3	1.1	1.2	27	0.01
KL46-02	422.5	425.5	0.0032		32	0.05	0.1	73	23	32	4	0.01	4	1.4	0.0	27	0.01
KL46-02	425.5	428.5	0.0049		49	0.04	0.1	137	22	61	15	0.01	4	1.6	1.6	29	0.01
KL46-02	428.5	431.5	0.0075		75	0.01	0.1	108	20	26	12	0.01	4	1.4	1.0	14	0.01
KL46-02	431.5	434.5	0.0019		19	0.02	0.1	81	61	33	3	0.01	3	1.2	1.4	30	0.01
KL46-02	434.5	437.5	0.0023		23	0.01	0.1	100	15	30	11	0.01	3	1.9	1.1	26	0.01
KL46-02	437.5	440.5	0.0018		18	0.02	0.1	180	21	25	4	0.01	4	2.8	2.1	30	0.01
KL46-02	440.5	443.5	0.0014		14	0.18	0.1	176	26	35	4	0.01	4	2.3	2.2	27	0.01
KL46-02	443.5	446.5	0.0026		26	0.08	0.1	234	23	54	16	0.01	4	4	3.3	36	0.01
KL46-02	446.5	449.5	0.0017		17	0.03	0.1	245	17	71	23	0.01	4	4.4	3.4	41	0.01
KL46-02	449.5	452.5	0.0025		25	0.03	0.1	199	19	45	18	0.01	3	3.9	3.2	23	0.01
KL46-02	452.5	455.5	0.0015		15	0.01	0.1	80	16	44	6	0.01	3	1.3	1.0	24	0.01
KL46-02	455.5	458.5	0.0028		28	0.05	0.1	80	15	74	39	0.01	2	1.2	0.9	31	0.01
KL46-02	458.5	461.5	0.0044		44	0.13	0.5	150	21	100	37	1	3	1.1	2.0	26	0.01
KL46-02	461.5	464.5	0.102		1020	0.12	0.8	98	19	74	9	0.01	4	1.2	4.1	39	0.01
KL46-02	464.5	467.5	0.0047		47	0.06	0.1	192	25	90	9	0.01	2	2.1	2.3	25	0.01
KL46-02	467.5	470.5	0.0071		71	0.03	0.1	76	15	64	3	0.01	2	1.1	1.5	18	0.1
KL46-02	470.5	473.2	0.062		620	0.12	0.8	115	21	61	9	0.01	2	1.3	3.7	18	0.01
KL46-02	473.2	476.5	1.25		12500	2.44	6.2	1730	17	160	320	78	38	2	16.0	53	0.01
KL46-02	476.5	479.5	1.2		12000	3.22	3.8	201	8	200	88	69	28	1.8	15.5	99	0.01
KL46-02	479.5	482.5	0.197		1970	0.99	0.8	193	21	80	220	4	10	1.6	3.8	44	0.01
KL46-02	482.5	485.5	0.098		980	0.47	1	173	54	120	113	4	8	2.9	3.3	82	0.01
KL46-02	485.5	488.5	0.072		720	0.27	0.7	292	101	120	500	1	8	2.9	3.2	54	0.01
KL46-02	488.5	491.5	0.116		1160	0.15	1.8	324	183	160	138	2	3	2.5	3.6	110	0.01
KL46-02	491.5	494.5	0.067		670	0.19	0.8	110	65	110	51	3	3	1.9	1.8	235	0.01
KL46-02	494.5	497.5	0.095		950	0.2	1.8	308	151	160	79	1	4	2.9	3.0	199	0.01
KL46-02	497.5	500.5	0.128		1280	0.2	1.6	119	137	320	81	2	8	3.7	3.9	215	0.01
KL46-02	500.5	503.5	0.068		680	0.2	1	132	53	170	40	1	3	2.5	3.2	81	0.01
KL46-02	503.5	505.6	0.28		2800	1.25	2.8	890	158	340	530	23	7	9.4	7.0	70	0.01
KL46-02	505.6	509.5	0.67		6700	1.1	3.9	1290	210	630	1125	15	22	7.8	9.8	75	0.01
KL46-02	509.5	512.5	3.06		30600	2.39	9.4	1940	140	480	204	12	50	7	61.3	192	0.14
KL46-02	512.5	515.5	0.89		8900	1.17	3.4	1410	110	1080	200	17	22	10.8	17.0	160	0.13
KL46-02	515.5	518.5	0.123		1230	0.71	0.8	324	105	360	95	1	4	8.8	6.1	80	0.01
KL46-02	518.5	521.5	0.098		980	0.89	0.7	1050	116	380	371	1	6	9.4	5.4	43	0.01
KL46-02	521.5	523.8	0.126		1260	3.41	15.5	2900	8480	625	215	11	6	30.1	16.6	128	0.14
KL46-02	523.8	525.4	0.0212		212	0.3	0.5	224	109	83	68	0.01	1	3	3.2	26	0.01
KL46-02	525.4	527.5	0.053		530	1.09	1.3	570	299	250	50	1	2	9.7	6.8	41	0.1
KL46-02	527.5	530.5	0.0087		87	0.23	0.8	162	115	52	15	0.01	2	4.6	5.1	21	0.01
KL46-02	530.5	533.5	0.02		200	0.33	0.7	122	75	70	33	0.01	2	4.8	5.6	27	0.01
KL46-02	533.5	536.5	0.0064		64	0.07	0.1	74	36	17	6	0.01	1	1	2.1	18	0.01
KL46-02	536.5	539.5	0.0082		82	0.17	0.1	312	58	41	11	0.01	1	1.9	4.7	22	0.01
KL46-02	539.5	542.5	0.0017		17	0.07	0.1	74	29	14	4	0.01	1	1.1	3.0	19	0.01
KL46-02	542.5	545.5	0.0029		29	0.04	0.1	89	99	15	10	0.01	1	0.7	2.0	16	0.01
KL46-02	545.5	548.5	0.022		220	0.3	0.1	131	36	120	39	2	2	1.8	5.0	50	0.01
KL46-02	548.5	551.5	0.0328		328	0.2	0.5	110	36	110	33	1	1	1.6	3.1	43	0.01
KL46-02	551.5	554.5	0.0064		64	0.05	0.1	103	41	46	11	0.01	1	1.1	2.3	25	0.01
KL46-02	554.5	557.5	0.0061		61	0.08	0.1	77	43	34	9	1	1	1.6	2.6	38	0.01
KL46-02	557.5	560.5	0.0201		201	0.11	0.5	144	39	60	20	6	1	1.5	4.2	35	0.01
KL46-02	560.5	563	0.0066		66	0.05	0.1	99	19	18	12	0.01	1	0.6	2.6	22	0.01
KL46-02	563	566.1	0.023		230	0.11	0.1	225	54	70	32	5	3	1.6	5.2	32	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL46-02	566.1	568	0.0026		26	0.03	0.1	36	17	10	6	0.01	1	0.5	1.4	12	0.01
KL46-02	568	571	0.0088		88	0.08	0.1	78	27	64	16	0.01	2	1.3	3.1	33	0.01
KL46-02	571	573.8	0.0031		31	0.08	0.6	100	37	73	9	0.01	2	1.7	4.2	43	0.12
KL46-02	573.8	574.8	0.0064		64	0.13	0.6	88	60	34	7	0.01	1	1.5	1.7	19	0.01
KL46-02	574.8	577.9	0.0009		9	0.03	4.6	920	1130	22	4	0.01	1	7	1.3	18	0.01
KL46-02	577.9	580.8	0.0005		5	0.07	0.1	55	32	22	4	0.01	1	0.7	1.5	21	0.01
KL46-02	580.8	582.7	0.0104		104	0.02	0.6	69	35	33	18	0.01	1	0.6	1.4	29	0.01
KL46-02	582.7	584.5	0.001		10	0.01	0.1	35	18	20	3	0.01	1	0.4	0.8	18	0.01
KL46-02	584.5	587.5	0.0029		29	0.02	0.1	42	18	17	4	0.01	1	0.3	1.1	18	0.01
KL46-02	587.5	590.5	0.0011		11	0.01	0.1	31	21	12	5	0.01	1	0.5	1.2	20	0.01
KL46-02	590.5	593.5	0.0005		5	0.01	0.1	16	12	9	5	0.01	1	0.2	0.6	17	0.01
KL46-02	593.5	596.5	0.0207		207	0.17	0.5	89	39	36	29	1	1	2.5	2.7	33	0.01
KL46-02	596.5	599.5	0.0042		42	0.11	1.1	63	470	28	14	0.01	1	2.9	6.0	27	0.01
KL46-02	599.5	602.5	0.0029		29	0.02	0.1	17	29	6	5	0.01	1	0.3	1.5	24	0.01
KL46-02	602.5	605.5	0.0022		22	0.01	0.1	38	15	4	3	0.01	1	0.2	1.1	24	0.01
KL46-02	605.5	608.5	0.003		30	0.02	0.1	80	17	8	2	0.01	1	0.5	2.8	22	0.01
KL46-02	608.5	611.5	0.0027		27	0.02	0.1	74	19	13	3	0.01	1	1.5	1.6	22	0.01
KL46-02	611.5	613.5	0.0057		57	0.01	1.7	92	23	19	2	0.01	1	1.8	2.6	21	0.01
KL46-02	613.5	616.6	0.0073		73	0.02	0.1	112	29	17	4	0.01	1	1.5	2.4	20	0.01
KL46-02	616.6	619.7	0.006		60	0.05	0.1	79	31	32	15	0.01	1	1.5	3.2	43	0.01
KL46-02	619.7	622.8	0.02		200	0.12	0.1	80	28	41	55	0.01	1	2.3	1.3	48	0.01
KL46-02	622.8	625.9	0.0018		18	0.02	0.1	26	16	13	2	0.01	1	0.3	0.6	29	0.01
KL46-02	625.9	629	0.001		10	0.01	0.1	10	12	10	3	0.01	1	0.2	1.0	23	0.01
KL46-02	629	632.1	0.0007		7	0.01	0.1	15	10	10	4	0.01	1	0.3	0.8	22	0.01
KL46-02	632.1	635.2	0.0021		21	0.06	1.2	24	32	25	5	0.01	1	6.2	1.5	21	0.01
KL46-02	635.2	637.6	0.0015		15	0.13	0.1	119	221	32	2	0.01	1	0.5	1.0	9	0.01
KL46-02	637.6	638.4	0.0009		9	0.01	0.1	22	18	4	1	0.01	1	0.3	0.8	14	0.01
KL46-02	638.4	641.4	0.0023		23	0.46	0.6	74	24	35	6	0.01	1	3.8	3.3	22	0.1
KL46-02	641.4	643.9	0.0008		8	0.01	0.1	172	230	6	3	0.01	1	0.3	1.5	17	0.01
KL46-02	643.9	644.5	0.0009		9	0.01	0.1	16	18	3	7	0.01	1	0.5	1.5	13	0.01
KL46-02	644.5	647.5	0.0006		6	0.01	0.1	34	14	4	3	0.01	1	0.2	1.1	15	0.01
KL46-02	647.5	650.5	0.0006		6	0.01	0.1	27	19	5	3	0.01	1	0.3	0.5	14	0.01
KL46-02	650.5	653.5	0.0009		9	0.01	0.1	32	18	4	2	0.01	1	0.2	1.3	14	0.01
KL46-02	653.5	656.5	0.0006		6	0.01	0.1	26	20	4	2	0.01	1	0.01	0.6	14	0.01
KL46-02	656.5	659.5	0.0004		4	0.01	0.1	24	13	4	1	0.01	1	0.2	0.8	18	0.01
KL46-02	659.5	662.5	0.0006		6	0.01	0.1	50	20	4	1	0.01	1	0.01	0.8	18	0.01
KL46-02	662.5	665.5	0.0004		4	0.04	0.1	61	20	8	1	0.01	1	0.2	1.4	12	0.01
KL46-03	0	3	0.009		90	0.01	0.1	21	16	2	3	0.01	1	0.3	0.0	17	0.01
KL46-03	3	6	0.0048		48	0.01	0.1	27	16	11	3	0.01	1	0.3	0.7	23	0.01
KL46-03	6	8.7	0.0034		34	0.01	0.1	41	11	12	2	0.01	1	0.3	1.2	21	0.01
KL46-03	8.7	10	0.0035		35	0.01	0.1	19	10	10	4	0.01	1	0.2	0.8	27	0.01
KL46-03	10	13	0.0008		8	0.01	0.1	20	13	12	3	0.01	1	0.01	0.0	22	0.01
KL46-03	13	16	0.0007		7	0.01	0.1	37	10	20	2	0.01	1	0.3	0.9	16	0.1
KL46-03	16	19	0.0017		17	0.01	0.1	33	12	30	4	0.01	1	0.5	1.4	21	0.21
KL46-03	19	22	0.0023		23	0.01	0.1	18	13	20	4	0.01	1	0.4	1.3	21	0.01
KL46-03	22	25	0.0073		73	0.01	0.1	15	15	10	3	0.01	1	0.5	0.7	14	0.01
KL46-03	25	28	0.0006		6	0.01	0.1	18	15	14	4	0.01	1	0.4	0.9	17	0.01
KL46-03	28	31	0.001		10	0.01	0.1	150	62	17	4	0.01	1	0.6	1.5	22	0.01
KL46-03	31	34	0.0007		7	0.02	0.1	19	18	14	4	0.01	1	0.6	1.4	16	0.15
KL46-03	34	37	0.0009		9	0.01	0.1	21	15	16	5	0.01	1	0.5	1.0	23	0.01
KL46-03	37	40	0.0008		8	0.01	0.1	25	17	18	5	0.01	1	0.4	1.1	19	0.01
KL46-03	40	43	0.0004		4	0.01	0.1	16	16	11	2	0.01	1	0.3	0.5	18	0.01
KL46-03	43	46	0.0003		3	0.01	0.1	12	12	10	3	0.01	1	0.3	0.0	19	0.01
KL46-03	46	49	0.0061		61	0.05	0.1	18	21	18	3	0.01	1	0.4	1.1	19	0.24
KL46-03	49	52	0.0006		6	0.01	0.1	23	15	9	1	0.01	1	0.6	1.4	16	0.1
KL46-03	52	55	0.0012		12	0.01	0.1	31	14	7	1	0.01	1	0.3	0.9	18	0.01
KL46-03	55	58	0.0002		2	0.01	0.1	16	13	10	3	0.01	1	0.6	0.6	32	0.01
KL46-03	58	61	0.0005		5	0.01	0.1	47	25	13	2	0.01	1	0.4	1.5	26	0.01
KL46-03	61	63.8	0.0005		5	0.01	0.1	17	15	11	1	0.01	1	0.6	0.8	19	0.01
KL46-03	63.8	66.9	0.0003		3	0.01	0.1	10	13	10	2	0.01	1	0.2	1.0	20	0.01
KL46-03	66.9	70	0.0003		3	0.01	0.1	18	14	17	1	0.01	1	0.2	1.0	17	0.01
KL46-03	70	73	0.0007		7	0.01	0.1	39	23	14	3	0.01	2	0.4	1.5	26	0.01
KL46-03	73	76	0.0004		4	0.01	0.6	26	26	18	2	0.01	2	0.4	1.0	32	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL46-03	76	79	0.0003		3	0.01	1.7	25	24	21	3	0.01	2	0.5	1.2	32	0.01
KL46-03	79	82	0.0015		15	0.01	0.1	40	23	14	3	0.01	1	0.5	0.8	34	0.01
KL46-03	82	85	0.0002		2	0.01	0.1	26	19	6	2	0.01	1	0.2	0.0	31	0.01
KL46-03	85	88	0.0003		3	0.01	0.1	96	21	4	1	0.01	1	0.2	1.2	24	0.01
KL46-03	88	91	0.0133		133	0.01	8.8	13300	3300	17	2	0.01	1	8.6	5.0	29	0.01
KL46-03	91	94	0.0013		13	0.01	0.1	100	41	13	2	0.01	1	0.3	0.9	24	0.1
KL46-03	94	96.6	0.0014		14	0.01	0.6	60	35	17	2	0.01	1	0.4	1.3	28	0.1
KL46-03	96.6	99.6	0.0019		19	0.01	0.1	22	21	17	4	0.01	1	0.4	1.3	28	0.01
KL46-03	99.6	102.7	0.0004		4	0.12	0.1	50	31	77	1	0.01	1	1	1.0	23	0.1
KL46-03	102.7	105.8	0.0007		7	0.14	0.6	76	100	100	1	0.01	1	1.6	1.4	27	0.22
KL46-03	105.8	108.9	0.0007		7	0.28	0.5	110	170	73	1	0.01	1	2.1	0.7	31	0.26
KL46-03	108.9	112	0.011		110	0.28	0.7	241	84	100	1	2	1	3.9	10.8	56	0.65
KL46-03	112	115	0.0032		32	0.16	0.1	174	63	52	1	1	1	1.8	3.2	25	0.19
KL46-03	115	118	0.0108		108	0.08	0.1	142	42	50	1	1	2	1.9	2.2	31	0.01
KL46-03	118	121	0.0121		121	0.04	0.1	65	36	21	1	78	1	1.7	8.3	34	0.01
KL46-03	121	124	0.001		10	0.6	0.6	203	70	230	2	4	3	2.4	3.9	60	0.26
KL46-03	124	127	0.0019		19	1.52	1.1	430	189	770	1	6	4	3.5	9.8	68	0.76
KL46-03	127	130	0.0017		17	0.34	0.1	104	35	170	7	1	3	2.4	2.3	68	0.42
KL46-03	130	133	0.0065		65	0.17	1.9	130	77	91	8	2	7	2	3.0	83	0.48
KL46-03	133	136	0.0035		35	0.07	3.9	34	60	68	2	1	7	1.5	2.8	50	0.12
KL46-03	136	139	0.062		620	0.91	12.9	1240	530	310	39	18	8	24	14.0	63	9.7
KL46-03	139	142	0.5		5000	1.26	259	18900	9200	1730	252	168	12	70	128.0	40	21
KL46-03	142	145	0.06		600	0.71	9.5	2670	430	250	89	61	7	24	17.7	29	5.91
KL46-03	145	148	0.193		1930	0.7	10.6	1990	327	700	87	43	7	78	9.5	23	3.94
KL46-03	148	151	0.0082		82	0.13	0.5	82	36	41	13	2	2	2.6	2.7	17	0.42
KL46-03	151	154	0.0156		156	0.05	1	268	56	57	14	4	3	2.3	2.8	13	0.39
KL46-03	154	157	0.0048		48	0.07	0.9	410	201	21	5	2	1	2.3	4.0	10	0.22
KL46-03	157	158.9	0.0242		242	0.18	0.9	99	38	130	104	66	3	3.9	3.0	61	0.51
KL46-03	158.9	161.4	0.0058		58	2.42	6.3	1750	1680	500	2360	180	7	19	18.3	148	1.56
KL46-03	161.4	163	0.0134		134	5.51	10.3	5300	5800	470	73	17	3	20.3	18.0	124	1.21
KL46-03	163	166	0.0023		23	0.59	0.7	216	225	72	10	2	2	2.5	1.8	131	0.41
KL46-03	166	169	0.0022		22	0.42	0.8	79	48	73	11	2	2	2.5	2.1	166	0.55
KL46-03	169	172	0.0027		27	3.04	2.5	163	274	370	104	25	4	16.8	6.0	142	2.91
KL46-03	172	175	0.0027		27	10.2	2.9	450	254	1340	1090	43	6	32	8.3	125	11.3
KL46-03	175	178	0.0012		12	1.04	1.6	1020	710	510	450	1	5	16.3	4.8	142	5.54
KL46-03	178	181	0.0019		19	0.35	0.7	182	134	310	132	0.01	4	8.2	2.2	238	2.95
KL46-03	181	184	0.0016		16	0.2	0.6	156	130	300	61	0.01	3	11.5	3.0	133	2.51
KL46-03	184	186.3	0.007		70	0.04	1.2	303	249	44	37	2	3	2.6	1.4	194	0.51
KL46-03	186.3	189.4	0.0013		13	0.02	0.1	170	91	69	40	0.01	2	2.1	1.0	158	0.32
KL46-03	189.4	191	0.0034		34	0.09	1.3	620	356	53	27	0.01	3	3.8	0.7	263	0.12
KL46-03	191	193	0.0013		13	0.03	0.6	186	114	150	110	0.01	3	3.5	1.7	150	0.37
KL46-03	193	196	0.0014		14	0.01	0.8	520	272	170	104	0.01	4	4.7	1.3	160	0.38
KL46-03	196	199	0.001		10	0.01	0.8	620	361	150	122	0.01	4	4.7	1.3	122	0.4
KL46-03	199	200.8	0.0011		11	0.01	0.1	147	70	160	187	1	3	3.2	1.5	154	0.36
KL46-03	200.8	202	0.0009		9	0.03	0.9	430	209	66	120	0.01	2	2.3	1.0	134	0.24
KL46-03	202	205	0.0013		13	0.09	0.8	510	229	330	211	4	5	8.1	2.8	139	0.66
KL46-03	205	208	0.0115		115	0.08	0.6	136	49	430	188	101	4	7.2	3.8	87	0.36
KL46-03	208	211	0.0051		51	0.07	0.5	156	90	400	745	78	4	4.5	3.3	116	0.01
KL46-03	211	214	0.012		120	0.19	1.3	346	119	210	276	35	3	3.8	2.1	36	0.1
KL46-03	214	217	0.162		1620	0.67	13.5	4240	1610	180	195	160	20	7.4	19.8	52	0.1
KL46-03	217	220	0.0075		75	0.09	2.4	580	660	26	9	7	3	1	3.9	23	0.01
KL46-03	220	223	0.007		70	0.07	2.3	1640	1150	26	4	1	2	1.9	4.0	19	0.1
KL46-03	223	226	0.0018		18	0.04	1.9	270	770	23	3	1	1	1.5	3.3	18	0.1
KL46-03	226	229	0.0035		35	0.21	3.2	1390	1100	53	9	3	1	4.9	4.8	39	0.18
KL46-03	229	232	0.014		140	0.57	6.9	6300	2300	120	43	32	2	12.8	28.5	62	0.37
KL46-03	232	235	0.0019		19	0.11	1.6	1280	820	31	3	2	1	4.7	1.6	21	0.2
KL46-03	235	238	0.0025		25	0.13	1.1	680	154	45	8	4	1	4.9	3.8	34	0.1
KL46-03	238	241	0.0018		18	0.33	0.7	690	356	53	8	4	2	6.9	2.5	28	0.34
KL46-03	241	244	0.0023		23	0.13	1.2	1440	950	28	5	5	1	3.5	5.0	24	0.17
KL46-03	244	247	0.0081		81	0.11	1.1	1880	1390	33	5	3	1	5.3	6.3	25	0.01
KL46-03	247	250	0.0048		48	0.14	6	3200	8200	42	18	0.01	1	11	39.5	41	0.16
KL46-03	250	252	0.0031		31	0.2	1.6	880	490	47	7	6	1	4.5	5.4	24	0.18
KL46-03	252	254	0.0018		18	0.36	1.6	480	285	31	3	2	1	5.1	5.3	27	0.17

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL46-03	254	257	0.0017		17	0.21	1.7	670	590	27	5	2	1	3.8	4.0	27	0.12
KL46-03	257	259	0.0011		11	0.05	0.9	241	140	14	2	2	1	1.3	2.5	20	0.01
KL46-03	259	262	0.0029		29	0.1	1.9	660	395	27	7	4	1	2.3	5.1	21	0.01
KL46-03	262	263	0.0012		12	0.05	1.4	158	144	17	2	2	1	1.3	1.1	21	0.01
KL46-03	263	266.5	0.0022		22	0.1	1.4	127	102	26	5	2	1	2	1.4	23	0.1
KL46-03	266.5	268	0.0019		19	0.16	1.8	550	388	34	4	2	1	3.4	6.3	26	0.01
KL46-03	268	271	0.0024		24	0.19	1.9	840	1030	31	4	3	1	4.7	7.1	25	0.1
KL46-03	271	274	0.0026		26	0.26	1.7	640	680	52	5	5	2	6.1	4.4	21	0.01
KL46-03	274	277	0.008		80	0.27	2	1370	960	41	4	3	1	12.1	3.8	18	0.37
KL46-03	277	280	0.0351		351	0.59	9.8	13800	14000	110	10	2	1	20.3	41.5	20	0.28
KL46-03	280	283	0.0029		29	0.35	2.3	1200	1680	31	4	0.01	1	5.8	9.5	19	0.11
KL46-03	283	286	0.0093		93	0.36	13.4	6100	7800	63	16	13	1	12.7	64.2	25	0.15
KL46-03	286	289	0.0027		27	0.28	1.1	391	193	30	11	0.01	1	2	4.4	26	0.01
KL46-03	289	292	0.0024		24	0.2	0.5	630	126	26	6	0.01	1	2.1	2.2	19	0.01
KL46-03	292	293.5	0.0006		6	0.06	0.1	109	98	10	1	0.01	1	0.5	0.0	11	0.01
KL46-03	293.5	296.5	0.0007		7	0.08	0.1	80	57	13	2	0.01	1	0.7	1.4	15	0.17
KL46-03	296.5	298.3	0.0071		71	0.49	3.2	580	230	230	25	0.01	7	9.9	12.3	60	0.55
KL46-03	298.3	301	0.0018		18	0.06	1	520	460	22	4	1	1	1.5	1.4	17	0.01
KL46-03	301	304	0.0104		104	0.07	1.2	780	790	51	13	2	1	2.6	2.7	17	0.1
KL46-03	304	307	0.0056		56	0.07	0.1	570	258	31	10	0.01	1	1.4	3.6	15	0.15
KL46-03	307	310	0.0025		25	0.18	0.1	177	85	52	7	0.01	1	2.7	1.5	23	0.27
KL46-03	310	313	0.001		10	0.08	0.1	187	79	29	7	0.01	1	1.4	2.7	18	0.16
KL46-03	313	316	0.0047		47	0.06	0.1	480	142	22	13	1	1	1.6	1.7	9	0.1
KL46-03	316	319	0.0073		73	0.18	0.8	670	301	31	40	2	1	5.5	6.5	17	0.31
KL46-03	319	322	0.0039		39	0.34	0.6	326	123	55	57	1	1	6	2.8	26	0.24
KL46-03	322	325	0.0219		219	0.28	2.4	5800	2600	110	65	3	3	7.9	34.3	24	0.13
KL46-03	325	328	0.0343		343	0.27	1.5	1100	550	72	55	6	2	7.2	19.1	31	0.45
KL46-03	328	331	0.015		150	0.24	0.9	900	349	78	47	4	1	5.2	9.9	39	0.4
KL46-03	331	334	0.0026		26	0.16	0.7	740	600	48	8	0.01	1	3.3	8.0	28	0.27
KL46-03	334	337	0.0056		56	0.1	2.9	1260	2520	53	7	2	1	5.4	18.4	35	0.21
KL46-03	337	340	0.0014		14	0.05	0.1	140	107	24	2	0.01	1	1.5	3.0	23	0.12
KL46-03	340	343	0.0049		49	0.09	2.5	3430	2240	30	12	21	1	2.5	55.5	31	0.1
KL46-03	343	346	0.0006		6	0.03	0.1	57	46	9	1	0.01	1	0.5	1.8	18	0.01
KL46-03	346	349	0.0005		5	0.01	0.1	28	14	17	1	0.01	1	0.6	0.0	11	0.01
KL46-03	349	352	0.0005		5	0.02	0.1	86	15	15	1	0.01	1	0.6	0.8	12	0.01
KL46-03	352	355	0.0016		16	0.01	0.1	27	17	19	2	0.01	1	0.5	0.9	13	0.01
KL46-03	355	358	0.0061		61	0.04	0.1	59	15	57	6	0.01	1	0.7	0.0	20	0.01
KL46-03	358	361	0.0009		9	0.01	0.1	26	12	6	1	0.01	1	0.2	0.0	13	0.01
KL46-03	361	364	0.0007		7	0.01	0.1	41	17	18	1	0.01	1	0.4	0.5	12	0.01
KL46-03	364	367	0.0008		8	0.02	0.1	63	25	3	1	0.01	1	0.3	0.7	13	0.01
KL46-03	367	370	0.0005		5	0.01	0.1	43	32	18	1	0.01	1	0.4	1.0	16	0.01
KL46-03	370	373	0.0006		6	0.01	0.1	23	15	7	1	0.01	1	0.3	0.6	13	0.01
KL46-03	373	376	0.0008		8	0.01	0.1	18	8	12	1	0.01	1	0.3	0.0	12	0.01
KL46-03	376	379	0.0018		18	0.01	0.1	21	9	9	1	0.01	1	0.2	0.5	14	0.01
KL46-03	379	382	0.0004		4	0.01	0.1	14	6	12	1	0.01	1	0.4	0.0	17	0.01
KL46-03	382	385	0.0009		9	0.01	0.1	24	9	13	3	0.01	1	0.3	0.7	13	0.01
KL46-03	385	387.1	0.0052		52	0.01	0.1	28	7	34	8	0.01	1	0.2	0.0	19	0.01
KL46-03	387.1	390.2	0.0005		5	0.01	0.1	26	22	20	2	0.01	1	0.2	0.8	14	0.01
KL46-03	390.2	393.3	0.0039		39	0.05	0.1	30	15	51	4	0.01	1	0.4	0.8	20	0.01
KL46-03	393.3	396.4	0.0019		19	0.03	0.1	27	14	26	1	0.01	1	0.8	0.5	16	0.01
KL46-03	396.4	399.5	0.0027		27	0.01	0.1	32	11	13	3	0.01	1	0.01	0.0	13	0.01
KL46-03	399.5	402.6	0.0398		398	0.07	0.1	80	15	50	157	41	1	0.4	1.8	26	0.01
KL46-03	402.6	405.7	0.0369		369	0.04	0.1	46	16	42	54	11	1	0.3	1.0	35	0.01
KL46-03	405.7	408.8	0.0148		148	0.03	0.1	48	17	68	11	1	1	0.5	0.0	33	0.01
KL46-03	408.8	411.9	0.0109		109	0.03	0.1	43	14	50	7	1	1	0.4	0.0	20	0.01
KL46-03	411.9	415	0.0091		91	0.02	0.1	45	18	52	7	1	1	0.01	0.0	29	0.01
KL46-03	415	418	0.0125		125	0.04	0.1	48	17	48	7	1	1	0.2	0.0	20	0.01
KL46-03	418	421	0.0266		266	0.07	0.1	56	19	66	53	4	1	0.6	0.5	26	0.01
KL46-03	421	424	0.0138		138	0.05	0.1	67	74	69	34	1	1	0.5	0.8	26	0.01
KL46-03	424	427	0.0041		41	0.01	0.1	38	19	50	7	0.01	1	0.3	0.0	19	0.01
KL46-03	427	430	0.0057		57	0.02	0.1	43	19	43	6	0.01	1	0.4	0.0	24	0.01
KL46-03	430	433	0.0099		99	0.03	0.1	68	18	85	8	2	3	0.4	0.0	35	0.01
KL46-03	433	436	0.0126		126	0.05	0.1	59	22	110	8	4	2	0.6	0.0	36	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL46-03	436	439	0.0108		108	0.05	0.1	52	18	120	5	1	3	0.6	0.0	32	0.01
KL46-03	439	442	0.0104		104	0.07	0.1	83	22	140	10	2	4	1	0.6	52	0.01
KL46-03	442	445	0.0056		56	0.04	0.1	36	19	78	5	0.01	1	0.6	0.0	25	0.01
KL46-03	445	448	0.0034		34	0.03	0.1	35	16	110	5	0.01	1	0.6	0.0	22	0.01
KL46-03	448	451	0.0018		18	0.03	0.1	33	15	81	4	0.01	1	0.6	0.5	29	0.1
KL46-03	451	454	0.0037		37	0.1	0.1	45	20	70	4	0.01	1	0.5	0.5	21	0.1
KL46-03	454	457	0.0041		41	0.05	0.1	48	19	47	12	0.01	1	0.5	0.0	26	0.01
KL46-03	457	460	0.0011		11	0.01	0.1	26	21	30	4	0.01	1	0.5	0.9	18	0.01
KL46-03	460	463	0.0041		41	0.01	0.1	27	31	48	5	0.01	1	0.3	0.0	15	0.01
KL46-03	463	466	0.0036		36	0.01	0.1	31	20	30	4	0.01	1	0.2	0.0	11	0.01
KL46-03	466	469	0.0018		18	0.01	0.1	15	14	11	2	0.01	1	0.01	0.7	6	0.01
KL46-03	469	472	0.0024		24	0.01	0.1	26	16	35	4	0.01	1	0.4	0.6	13	0.01
KL46-03	472	475	0.001		10	0.01	0.1	39	19	27	7	0.01	1	0.4	0.6	16	0.01
KL46-03	475	478	0.0006		6	0.01	0.1	24	16	38	2	0.01	1	0.9	0.0	16	0.01
KL46-03	478	481	0.0014		14	0.02	0.1	25	16	50	3	0.01	1	0.6	1.0	15	0.01
KL46-03	481	484	0.0048		48	0.03	0.1	59	17	55	3	0.01	1	0.5	0.9	20	0.01
KL46-03	484	487	0.065		650	0.71	0.1	32	18	52	4	0.01	2	0.4	1.9	19	0.01
KL46-03	487	489.2	1.11		11100	4.2	4.6	116	24	120	10	9	21	2	14.8	43	0.01
KL46-03	489.2	492.3	0.064		640	0.13	0.1	34	16	84	125	0.01	1	1.5	1.4	24	0.1
KL46-03	492.3	495.4	0.2		2000	0.33	1.5	113	35	200	470	36	12	4.4	4.3	69	0.18
KL46-03	495.4	498.5	0.0238		238	0.96	0.9	1150	398	160	930	65	10	4.7	4.9	94	0.38
KL46-03	498.5	501.5	0.0065		65	0.13	0.1	68	20	180	620	2	5	3.1	1.3	94	0.11
KL46-03	501.5	503.2	0.019		190	0.16	0.1	102	16	190	1100	1	13	4.9	1.6	45	0.12
KL46-03	503.2	505	0.105		1050	0.11	0.7	74	15	100	113	3	1	1.3	2.5	21	0.14
KL46-03	505	508	0.0146		146	0.05	0.1	98	82	100	27	1	1	1.5	1.4	23	0.1
KL46-03	508	511	0.148		1480	0.09	0.8	118	10	160	1080	2	10	2.3	3.1	90	0.01
KL46-03	511	514	0.0224		224	0.12	0.1	97	12	81	2270	2	7	3	3.8	128	0.1
KL46-03	514	517	0.158		1580	0.24	1	104	21	220	2875	9	6	3.5	4.6	77	0.14
KL46-03	517	520	0.346		3460	0.41	6	1710	101	140	980	4	14	4.2	3.8	80	0.13
KL46-03	520	523	0.011		110	0.31	0.1	176	16	87	36	0.01	2	4.7	6.3	85	0.4
KL46-03	523	526	0.0053		53	0.09	0.1	37	15	33	29	0.01	1	2.6	3.5	28	0.11
KL46-03	526	529	0.071		710	0.09	0.7	240	24	84	13	0.01	3	2.3	2.8	43	0.01
KL46-03	529	532	0.0122		122	0.02	0.1	52	17	8	23	0.01	1	0.5	1.4	34	0.01
KL46-03	532	535	0.204		2040	0.05	0.6	102	22	35	8	2	1	1	3.2	20	0.01
KL46-03	535	538	0.005		50	0.19	0.1	73	10	71	4	1	1	2.9	3.6	27	0.15
KL46-03	538	541	0.0071		71	0.02	0.1	69	11	23	2	1	1	1.1	3.5	15	0.01
KL46-03	541	543	0.0056		56	0.05	0.1	26	14	36	9	1	1	1	1.2	13	0.01
KL46-03	543	547	0.0037		37	0.04	0.1	42	10	35	88	1	1	1.4	1.2	42	0.01
KL46-03	547	549	0.0063		63	0.11	0.1	38	8	54	106	1	4	1.8	0.7	83	0.01
KL46-03	549	551	0.0068		68	0.08	0.1	28	8	37	44	1	7	1.5	0.6	114	0.01
KL46-03	551	553	0.0073		73	0.06	0.1	36	12	27	6	2	1	1	0.7	124	0.01
KL46-03	553	556	0.0098		98	0.32	0.5	290	31	67	28	17	1	3.2	3.9	134	0.01
KL46-03	556	559	0.048		480	1.6	10.5	4300	1380	320	31	140	1	12.5	8.8	109	0.13
KL46-03	559	562	0.0178		178	0.07	0.1	38	12	44	7	1	1	1.3	1.2	142	0.01
KL46-03	562	564	0.0074		74	0.27	1.4	710	109	120	41	22	4	2.8	7.3	132	0.01
KL46-03	564	565.8	0.0112		112	0.07	0.1	48	19	61	9	1	1	1.6	1.5	113	0.01
KL46-04	0	3.5	0.039		390	0.01	0.1	34	14	6	8	0.01	1	0.3	1.9	43	0.01
KL46-04	3.5	6.5	0.0078		78	0.05	0.1	28	17	5	4	0.01	1	0.4	1.5	24	0.01
KL46-04	6.5	9.5	0.0068		68	0.02	0.1	60	38	4	5	0.01	1	1.2	1.4	28	0.01
KL46-04	9.5	12.5	0.0062		62	0.04	0.1	48	31	8	5	0.01	1	1.1	1.2	26	0.01
KL46-04	12.5	15.5	0.004		40	0.22	0.7	66	27	17	2	0.01	1	1.6	1.2	28	0.55
KL46-04	15.5	18.5	0.0041		41	0.06	0.1	79	28	16	10	0.01	1	2	1.6	40	0.1
KL46-04	18.5	21.5	0.0036		36	0.04	0.1	56	21	15	9	0.01	1	1.2	1.2	45	0.01
KL46-04	21.5	24.5	0.0016		16	0.01	0.1	21	11	9	3	0.01	1	0.3	0.6	42	0.01
KL46-04	24.5	27.5	0.0013		13	0.01	0.1	52	16	13	2	0.01	1	0.5	1.3	20	0.01
KL46-04	27.5	30.5	0.009		90	0.04	0.1	28	23	14	4	0.01	1	0.9	1.1	37	0.16
KL46-04	30.5	33.5	0.0317		317	0.14	1.6	1080	123	120	13	3	2	8.2	5.4	62	0.21
KL46-04	33.5	36.5	0.0013		13	0.01	0.1	51	33	24	5	1	2	2.2	2.2	25	0.1
KL46-04	36.5	39.5	0.0038		38	0.04	0.1	26	26	21	3	0.01	1	1.1	1.4	35	0.11
KL46-04	39.5	42.5	0.0033		33	0.04	0.1	54	24	9	3	0.01	1	0.6	1.4	25	0.01
KL46-04	42.5	45.5	0.0006		6	0.01	0.1	16	17	5	3	0.01	1	0.2	0.5	20	0.01
KL46-04	45.5	48.5	0.0039		39	0.03	0.1	51	20	4	2	0.01	1	0.4	1.1	24	0.1
KL46-04	48.5	50.6	0.0012		12	0.01	0.1	55	34	6	1	0.01	1	0.9	0.6	17	0.22

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL46-04	50.6	53.7	0.002		20	0.23	0.8	172	69	14	3	0.01	1	4.5	3.1	25	0.15
KL46-04	53.7	56.8	0.0011		11	0.19	0.8	820	173	37	2	0.01	1	1.9	3.1	24	0.8
KL46-04	56.8	59.9	0.0012		12	0.05	0.1	34	36	17	3	0.01	1	0.9	1.3	37	0.14
KL46-04	59.9	63	0.0014		14	0.06	0.1	48	25	11	4	0.01	1	0.9	1.4	31	0.14
KL46-04	63	66	0.0009		9	0.09	0.1	202	46	6	2	0.01	1	1.3	2.3	27	0.29
KL46-04	66	69.2	0.0017		17	0.13	0.1	13	14	4	3	0.01	1	0.4	1.4	29	0.12
KL46-04	69.2	72.3	0.0021		21	0.18	0.7	73	36	18	3	0.01	1	1.7	3.2	31	0.24
KL46-04	72.3	75.4	0.001		10	0.1	0.6	341	82	11	2	0.01	1	1.8	2.6	24	0.53
KL46-04	75.4	78.5	0.0073		73	0.11	0.1	118	48	15	22	0.01	1	3.2	2.2	31	0.2
KL46-04	78.5	81.5	0.0009		9	0.04	0.1	20	17	12	7	0.01	1	0.7	1.3	34	0.25
KL46-04	81.5	84.5	0.0018		18	0.05	0.1	32	19	11	19	0.01	1	1	1.4	26	0.32
KL46-04	84.5	87.5	0.0167		167	0.09	0.1	28	16	12	4	0.01	1	0.6	1.6	48	0.27
KL46-04	87.5	90.5	0.0011		11	0.12	0.1	76	22	35	4	0.01	1	1.1	1.9	37	0.5
KL46-04	90.5	93.5	0.0007		7	0.13	0.1	56	22	46	2	0.01	1	1.2	1.8	50	0.45
KL46-04	93.5	95.4	0.0362		362	0.12	2	1250	135	130	16	3	2	9.2	6.8	83	0.21
KL46-04	95.4	97.8	0.0012		12	0.13	0.1	29	20	16	2	0.01	1	0.9	1.6	32	0.22
KL46-04	97.8	99.2	0.0009		9	0.17	0.1	45	27	12	1	0.01	1	1.9	1.9	27	0.26
KL46-04	99.2	102.3	0.0016		16	0.08	0.1	87	32	15	4	0.01	1	1.9	2.0	46	0.18
KL46-04	102.3	105.4	0.0065		65	0.15	3.3	1850	1240	73	3	0.01	1	7.4	8.1	30	0.47
KL46-04	105.4	108.5	0.0016		16	0.21	0.1	100	77	44	3	0.01	2	2	3.6	28	0.49
KL46-04	108.5	111.5	0.0006		6	0.01	0.1	18	20	6	2	0.01	1	0.6	2.6	22	0.01
KL46-04	111.5	114.5	0.0011		11	0.01	0.1	49	29	7	2	0.01	1	1.9	2.1	36	0.01
KL46-04	114.5	117.5	0.001		10	0.01	0.1	48	33	5	3	0.01	1	0.5	1.5	37	0.01
KL46-04	117.5	120.5	0.0037		37	0.01	0.1	111	25	13	4	0.01	1	0.8	1.0	29	0.01
KL46-04	120.5	123.5	0.021		210	0.06	1.2	1710	78	100	12	2	1	6.3	4.6	41	0.14
KL46-04	123.5	126.5	0.0013		13	0.01	0.1	46	19	8	7	0.01	1	1	1.6	22	0.01
KL46-04	126.5	129.5	0.0076		76	0.03	0.1	219	37	27	6	0.01	1	2.4	1.5	30	0.01
KL46-04	129.5	132.5	0.001		10	0.01	0.1	16	16	3	3	0.01	1	0.3	0.8	22	0.01
KL46-04	132.5	135.5	0.0035		35	0.1	0.1	299	109	41	76	5	3	3.4	3.1	48	0.1
KL46-04	135.5	138.5	0.003		30	0.15	0.1	69	34	30	5	0.01	2	2.4	1.7	37	0.36
KL46-04	138.5	141.5	0.002		20	0.02	1.1	180	450	38	3	2	1	2.7	14.0	36	0.1
KL46-04	141.5	144.5	0.0009		9	0.01	0.1	145	156	44	6	0.01	1	3.8	3.6	53	0.23
KL46-04	144.5	147.5	0.0026		26	0.12	0.1	64	32	28	4	0.01	2	2.3	2.3	41	0.32
KL46-04	147.5	150.5	0.0009		9	0.06	0.1	73	34	47	3	1	3	2.6	3.7	63	0.15
KL46-04	150.5	152.2	0.0042		42	0.07	0.1	36	28	28	5	1	5	1.7	3.4	110	0.01
KL46-04	152.2	155	0.068		680	0.18	20.4	44000	19600	73	18	14	4	16.5	314.0	38	0.15
KL46-04	155	157.3	0.0043		43	0.07	0.1	154	106	23	31	3	7	2	3.0	66	0.01
KL46-04	157.3	158.6	0.0218		218	0.14	7.8	4600	2900	96	53	46	1	16	58.0	48	0.2
KL46-04	158.6	161.7	0.181		1810	0.52	9.6	6000	520	780	65	16	4	55	28.0	130	0.72
KL46-04	161.7	163.6	0.0312		312	0.45	6.7	1480	710	220	18	28	1	60	8.6	181	0.72
KL46-04	163.6	166.7	0.0154		154	0.84	3.8	296	222	480	162	44	3	56	8.5	73	1
KL46-04	166.7	168.5	0.0025		25	0.19	1	195	136	110	52	8	2	7.6	2.5	76	0.13
KL46-04	168.5	171.5	0.0048		48	0.6	1.5	1400	353	210	500	34	3	24	5.8	86	0.28
KL46-04	171.5	174.5	0.0019		19	0.16	0.1	324	98	66	82	3	1	4.1	2.0	110	0.1
KL46-04	174.5	177.5	0.0096		96	0.14	0.6	112	63	70	29	6	3	8.6	1.8	221	0.1
KL46-04	177.5	180	0.0017		17	0.07	0.1	60	27	61	30	0.01	2	4.2	0.0	90	0.01
KL46-04	180	182.9	0.0016		16	0.11	0.1	126	37	150	27	2	2	6.4	1.1	50	0.12
KL46-04	182.9	186	0.0017		17	0.09	0.1	63	21	51	5	6	2	2.1	0.0	206	0.01
KL46-04	186	189.1	0.0415		415	0.65	2.6	710	321	330	1140	6	7	9.5	6.8	42	0.3
KL46-04	189.1	192.2	0.0019		19	0.35	0.1	148	40	190	85	8	3	4.1	1.9	200	0.12
KL46-04	192.2	194	0.0025		25	0.34	0.1	110	36	140	109	0.01	2	3.8	1.2	127	0.2
KL46-04	194	197	0.0021		21	0.2	0.7	208	56	150	112	2	3	3.3	1.0	51	0.13
KL46-04	197	198.5	0.143		1430	0.34	8.2	9200	460	400	95	1	3	26.5	21.5	49	0.5
KL46-04	198.5	200.7	0.0028		28	0.86	1.1	284	126	310	1180	3	3	6.5	4.7	47	0.32
KL46-04	200.7	203.2	0.0018		18	0.06	0.1	76	28	56	15	6	3	3.3	0.6	114	0.01
KL46-04	203.2	204.5	0.0048		48	0.47	1.1	620	219	300	900	3	7	11.1	9.1	38	0.4
KL46-04	204.5	207.5	0.0145		145	1.11	4.6	1600	1140	440	1170	11	7	16.6	10.4	128	0.72
KL46-04	207.5	210.5	0.3		3000	1	38	40000	14200	1670	1150	150	12	155	55.0	88	2.21
KL46-04	210.5	212.8	0.0076		76	0.13	4.5	2100	910	95	180	28	2	8	11.4	65	0.11
KL46-04	212.8	215.9	0.0025		25	0.05	0.6	138	119	26	6	3	1	3.1	3.2	30	0.01
KL46-04	215.9	219	0.0029		29	0.14	0.7	980	235	38	13	1	1	4	2.6	26	0.14
KL46-04	219	222.1	0.0065		65	0.14	0.6	143	93	92	35	6	1	8	2.0	173	0.16
KL46-04	222.1	225.2	0.0047		47	0.17	0.6	650	115	73	57	6	1	4.5	2.7	37	0.16

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL46-04	225.2	227.6	0.0016		16	0.04	0.1	163	138	25	18	2	1	2.7	1.7	23	0.01
KL46-04	227.6	229.2	0.01		100	0.14	2.3	660	560	76	8	10	1	30	5.3	80	0.23
KL46-04	229.2	230.9	0.0071		71	0.05	1.6	303	220	32	2	14	1	4.4	5.5	23	0.01
KL46-04	230.9	232	0.0022		22	0.04	2.1	530	1790	15	6	3	1	4.6	7.0	21	0.01
KL46-04	232	234	0.0018		18	0.03	2.2	590	2300	9	6	4	1	4.2	9.6	18	0.01
KL46-04	234	237.2	0.0112		112	0.04	0.1	347	54	48	5	1	1	2.6	2.3	37	0.01
KL46-04	237.2	240.2	0.0022		22	0.06	0.6	148	178	31	5	3	1	2.5	1.5	21	0.01
KL46-04	240.2	243.3	0.0018		18	0.06	0.1	195	258	22	12	2	1	2.5	1.5	12	0.01
KL46-04	243.3	245.7	0.007		70	0.05	1.5	420	398	59	5	8	1	8.8	4.3	28	0.01
KL46-04	245.7	248.3	0.0361		361	0.06	2.3	146	207	130	6	2	1	18.9	2.9	25	0.13
KL46-04	248.3	251.3	0.0038		38	0.05	0.8	135	139	18	5	7	1	3	2.1	21	0.01
KL46-04	251.3	253	0.0015		15	0.01	0.1	80	104	9	2	2	1	1.2	1.4	23	0.01
KL46-04	253	255	0.0017		17	0.09	0.1	179	56	37	42	2	1	3.3	1.8	65	0.1
KL46-04	255	257.6	0.174		1740	0.07	7.6	318	156	650	14	9	2	46	3.4	25	0.47
KL46-04	257.6	260.7	0.0023		23	0.04	0.1	73	117	23	22	2	2	1.4	2.4	22	0.01
KL46-04	260.7	262	0.006		60	0.05	0.1	81	216	25	5	1	1	3.3	2.3	24	0.01
KL46-04	262	265	0.0049		49	0.09	0.1	490	248	20	19	2	1	4.4	2.1	13	0.01
KL46-04	265	266.9	0.0311		311	0.29	1.2	2070	364	120	70	12	2	20	4.0	20	0.13
KL46-04	266.9	270	0.0055		55	0.09	0.6	173	118	49	6	5	1	3.4	1.4	31	0.1
KL46-04	270	273.1	0.0023		23	0.05	1	304	630	20	4	4	1	2.1	6.2	29	0.01
KL46-04	273.1	276	0.0011		11	0.03	0.1	77	126	13	6	2	1	1	1.7	25	0.01
KL46-04	276	278.1	0.0039		39	0.04	0.1	90	75	12	7	4	1	2.2	1.2	23	0.01
KL46-04	278.1	279.5	0.0011		11	0.04	0.1	194	112	15	11	2	1	1.5	1.6	27	0.01
KL46-04	279.5	282.6	0.0012		12	0.02	0.1	56	41	6	4	0.01	1	0.6	0.7	21	0.01
KL46-04	282.6	285.5	0.0011		11	0.04	0.1	192	155	9	5	3	1	1.6	1.9	15	0.01
KL46-04	285.5	288	0.0015		15	0.04	0.9	334	460	6	17	3	1	2.8	3.7	15	0.01
KL46-04	288	291.1	0.0015		15	0.01	1.3	390	1140	6	9	3	1	0.01	0.0	14	0.01
KL46-04	291.1	293.7	0.0017		17	0.02	0.1	810	406	3	7	1	1	2.9	1.9	10	0.01
KL46-04	293.7	296.1	0.0016		16	0.03	0.8	396	960	9	9	2	1	2.5	2.9	10	0.01
KL46-04	296.1	298.4	0.0041		41	0.03	0.7	880	860	10	15	2	1	4.4	2.9	16	0.01
KL46-04	298.4	300.5	0.0023		23	0.02	24.4	2190	35800	8	6	0.01	1	35.8	3.0	18	0.01
KL46-04	300.5	303.5	0.0057		57	0.04	1	960	1290	25	15	2	1	5.1	3.3	18	0.01
KL46-04	303.5	306.2	0.0027		27	0.04	0.1	218	620	21	5	1	1	3.3	1.9	17	0.01
KL46-04	306.2	307.2	0.0012		12	0.03	0.5	267	770	36	12	3	1	2.9	2.0	48	0.01
KL46-04	307.2	309.5	0.0017		17	0.02	1.6	670	960	7	13	7	1	3.1	9.1	11	0.01
KL46-04	309.5	311.1	0.0012		12	0.03	0.1	336	500	9	16	0.01	1	2.5	1.4	9	0.01
KL46-04	311.1	312.5	0.0015		15	0.02	0.1	305	336	6	6	0.01	1	2.2	1.6	11	0.01
KL46-04	312.5	315.4	0.0083		83	0.19	7.7	372	4030	97	29	31	1	26.3	50.0	30	0.01
KL46-04	315.4	318.5	0.0022		22	0.05	1	84	143	21	5	8	1	1.9	2.4	22	0.01
KL46-04	318.5	321.4	0.0016		16	0.02	0.1	177	313	12	4	5	1	2.1	1.5	15	0.01
KL46-04	321.4	324.5	0.0012		12	0.01	0.1	246	400	2	4	0.01	1	1.9	1.0	8	0.01
KL46-04	324.5	327.5	0.0013		13	0.01	0.1	297	314	6	5	0.01	1	1.9	1.3	12	0.01
KL46-04	327.5	330.5	0.24		2400	0.08	3.7	5110	660	800	34	28	5	106	3.7	22	0.3
KL46-04	330.5	333.5	0.0145		145	0.04	0.1	760	650	62	8	2	1	8.6	2.2	13	0.1
KL46-04	333.5	336.5	0.0324		324	0.23	1.2	3560	1570	180	7	1	3	18.9	7.3	9	0.25
KL46-04	336.5	338.9	0.0077		77	0.08	5.3	6800	8700	35	5	1	1	16	12.4	21	0.13
KL46-04	338.9	342	0.0077		77	0.08	5.3	6800	8700	35	5	1	1	16	12.4	21	0.13
KL46-04	342	345.1	0.0048		48	0.02	0.6	5240	1400	32	3	1	1	7.5	4.5	24	0.01
KL46-04	345.1	348.2	0.0032		32	0.08	2.3	5180	5400	46	9	1	1	10.1	8.4	16	0.19
KL46-04	348.2	351.3	0.0035		35	0.06	0.1	1240	530	36	5	0.01	1	3.3	3.4	16	0.01
KL46-04	351.3	354.4	0.0074		74	0.11	0.1	1090	382	61	8	0.01	1	3.2	2.4	17	0.16
KL46-04	354.4	357.5	0.0039		39	0.16	0.1	1040	186	72	9	1	3	3.8	2.3	24	0.1
KL46-04	357.5	360.5	0.0043		43	0.08	0.1	1140	550	72	11	1	2	5	1.9	16	0.1
KL46-04	360.5	363.5	0.0019		19	0.07	0.1	890	123	57	6	0.01	1	2.6	1.4	15	0.01
KL46-04	363.5	366.5	0.0047		47	0.05	0.1	2140	399	39	8	1	1	4	1.7	13	0.01
KL46-04	366.5	369.5	0.0047		47	0.05	0.1	2140	399	39	8	1	1	4	1.7	13	0.01
KL46-04	369.5	372.5	0.0049		49	0.13	0.1	1430	203	110	4	1	2	5.3	2.9	15	0.25
KL46-04	372.5	375.5	0.0061		61	0.08	1.1	7000	1410	28	7	3	1	1.8	3.3	12	0.1
KL46-04	375.5	378.5	0.0059		59	0.19	0.1	1540	283	52	11	0.01	1	4.2	2.1	16	0.18
KL46-04	378.5	381.5	0.0058		58	0.04	0.1	540	176	28	5	0.01	1	1.4	1.9	10	0.01
KL46-04	381.5	384.5	0.0102		102	0.24	0.1	1260	369	140	12	0.01	3	7.6	3.7	20	0.27
KL46-04	384.5	387.5	0.0084		84	0.1	0.1	560	194	38	6	0.01	1	3.8	1.3	11	0.19
KL46-04	387.5	390.5	0.007		70	0.08	0.1	700	181	27	6	1	2	3.2	1.8	12	0.18

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL46-04	390.5	393.5	0.0014	14	0.07	0.1	850	72	42	3	0.01	1	4.2	1.3	16	0.23
KL46-04	393.5	396.5	0.0074	74	0.05	2.4	7900	4900	35	4	5	1	15.3	18.5	11	0.29
KL46-04	396.5	399.5	0.0071	71	0.08	0.1	1020	141	28	6	2	2	2.6	1.1	13	0.16
KL46-04	399.5	402.4	0.0039	39	0.03	0.7	1730	1610	25	2	0.01	1	9	4.7	11	0.1
KL46-04	402.4	405.5	0.0032	32	0.07	0.1	2150	229	40	3	0.01	1	3.8	3.3	16	0.11
KL46-04	405.5	408.5	0.0011	11	0.05	0.1	1580	243	29	3	0.01	1	3.9	2.0	13	0.1
KL46-04	408.5	411.5	0.0019	19	0.05	0.1	1020	343	12	6	0.01	1	1.7	1.3	14	0.01
KL46-04	411.5	414.5	0.0014	14	0.11	0.1	520	180	42	6	0.01	2	2.4	2.2	19	0.01
KL46-04	414.5	417	0.0187	187	0.05	0.1	278	82	19	6	0.01	1	0.9	1.6	11	0.01
KL46-04	417	420.1	0.0018	18	0.06	0.1	1040	161	22	8	0.01	1	1.2	1.8	7	0.1
KL46-04	420.1	422	0.0061	61	0.09	0.1	1840	108	37	7	0.01	1	3.7	0.8	15	0.16
KL46-04	422	423.5	0.082	820	0.16	1.3	1580	520	330	21	2	7	38	5.0	33	0.79
KL46-04	423.5	426.3	0.22	2200	0.34	3.5	5940	1600	880	49	3	15	51	5.3	45	1.77
KL46-04	426.3	429.4	0.147	1470	0.5	1.7	8000	510	520	630	0.01	8	23	2.8	66	1.51
KL46-04	429.4	432.5	0.0122	122	0.1	0.1	900	77	51	1180	0.01	4	3	1.8	100	0.17
KL46-04	432.5	435.5	0.0132	132	0.16	0.5	352	51	68	1240	0.01	4	4.6	1.1	106	0.22
KL46-04	435.5	438.5	0.011	110	0.13	0.1	293	45	63	980	0.01	6	2	1.1	72	0.11
KL46-04	438.5	441.5	0.0104	104	0.08	0.1	430	76	64	310	0.01	3	2	1.2	70	0.1
KL46-04	441.5	444.5	0.149	1490	0.1	0.1	145	40	41	136	0.01	2	2.1	1.6	63	0.01
KL46-04	444.5	447.5	0.0355	355	0.03	0.1	160	18	20	89	0.01	7	0.4	1.0	23	0.01
KL46-04	447.5	450.5	0.3	3000	0.17	0.9	650	408	410	118	1	4	43	3.6	40	0.19
KL46-04	450.5	452.8	0.126	1260	0.05	0.8	410	90	25	25	0.01	6	3.1	1.8	36	0.01
KL46-04	452.8	455.9	0.24	2400	0.14	0.9	1850	315	560	22	2	4	40	4.4	36	0.01
KL46-04	455.9	459	0.047	470	0.03	0.1	1060	93	58	90	0.01	2	2.6	2.2	53	0.01
KL46-04	459	462.1	0.26	2600	0.15	0.5	194	22	10	24	0.01	4	0.3	2.2	16	0.01
KL46-04	462.1	465.2	0.44	4400	0.16	2.4	78	35	10	37	6	16	1.3	8.5	97	0.01
KL46-04	465.2	468.3	0.148	1480	0.06	0.5	141	34	15	147	0.01	3	0.6	1.2	38	0.01
KL46-04	468.3	471.4	0.3	3000	0.16	1.5	770	335	320	121	2	6	35	2.4	47	0.12
KL46-04	471.4	474.5	0.148	1480	0.09	0.5	214	51	82	17	1	3	3.9	1.3	23	0.1
KL46-04	474.5	477.5	0.21	2100	0.11	0.7	267	22	18	16	0.01	4	0.7	2.2	22	0.01
KL46-04	477.5	480.5	0.09	900	0.05	0.1	38	19	8	16	0.01	3	0.2	1.1	20	0.01
KL46-04	480.5	483.5	0.127	1270	0.04	0.6	261	29	49	159	0.01	4	1.3	1.9	47	0.01
KL46-04	483.5	486.5	0.156	1560	0.05	0.7	117	11	10	153	0.01	5	0.01	1.6	16	0.01
KL46-04	486.5	489.5	0.181	1810	0.14	0.7	251	12	13	7	0.01	4	0.7	1.7	24	0.01
KL46-04	489.5	492.5	0.28	2800	0.16	1.6	226	41	52	4	3	6	1	2.9	32	0.01
KL46-04	492.5	495.5	0.83	8300	0.47	1.1	1030	218	1140	8	0.01	10	19.1	16.0	83	0.41
KL46-04	495.5	498.5	0.8	8000	0.8	1.6	80	20	23	255	2	5	1.7	6.3	27	0.01
KL46-04	498.5	501.5	0.9	9000	0.57	1.1	308	96	100	70	0.01	13	1.5	9.8	68	0.01
KL46-04	501.5	504.5	0.96	9600	0.76	1.1	570	59	230	25	0.01	9	2.5	10.3	43	0.01
KL46-04	504.5	507.5	0.27	2700	0.28	0.9	590	450	190	39	1	7	35	3.3	52	0.33
KL46-04	507.5	510.5	0.5	5000	0.25	0.6	181	37	25	13	0.01	8	1	3.7	32	0.01
KL46-04	510.5	513.5	0.42	4200	0.16	0.5	95	20	12	6	0.01	9	1	3.5	30	0.01
KL46-04	513.5	515.6	0.176	1760	0.14	0.1	25	13	3	15	0.01	2	0.3	1.5	12	0.01
KL46-04	515.6	518	0.0226	226	0.04	0.1	72	34	9	9	0.01	1	0.6	0.8	32	0.01
KL46-04	518	519.5	0.52	5200	0.34	1	1290	400	1370	91	4	11	20.8	6.2	64	0.26
KL46-04	519.5	521.7	0.046	460	0.33	0.5	2660	520	140	68	0.01	8	3.3	10.7	74	0.14
KL46-04	521.7	522.9	0.109	1090	0.06	0.1	95	63	16	14	0.01	5	1.3	2.1	75	0.01
KL46-04	522.9	524	0.75	7500	0.53	1.1	375	204	69	21	0.01	15	14.1	7.5	60	0.13
KL46-04	524	525.3	0.56	5600	0.15	0.1	136	29	16	6	0.01	15	0.3	4.3	27	0.01
KL46-04	525.3	528.4	1.2	12000	0.55	1.4	266	35	10	3	1	24	0.5	10.3	23	0.01
KL46-04	528.4	530.7	0.82	8200	0.53	0.9	394	203	65	18	0.01	18	11.6	8.8	56	0.15
KL46-04	530.7	533.8	1.1	11000	0.49	1.5	247	127	20	14	0.01	21	1.2	10.0	23	0.01
KL46-04	533.8	535.9	0.36	3600	1.34	0.9	1220	202	190	14	1	20	5.7	9.8	21	0.11
KL46-04	535.9	537.5	1.23	12300	0.45	1.3	328	34	2	1	1	19	0.2	12.5	28	0.01
KL46-04	537.5	540.5	1.35	13500	0.6	0.9	149	28	0.01	2	0.01	19	0.01	8.0	28	0.01
KL46-04	540.5	543.5	1.49	14900	0.62	1.4	113	16	4	1	0.01	16	0.01	10.5	32	0.01
KL46-04	543.5	546.5	1.07	10700	0.69	1.3	500	50	170	14	0.01	9	1.3	8.0	55	0.01
KL46-04	546.5	549.5	0.363	3630	0.17	1.6	950	82	280	45	3	14	15.3	5.5	71	0.01
KL46-04	549.5	552.5	4.35	43500	1.76	3.6	227	94	3	2	0.01	23	0.01	16.0	32	0.01
KL46-04	552.5	555.5	1.62	16200	0.68	1.3	243	35	10	13	0.01	16	0.4	10.0	36	0.01
KL46-04	555.5	558.5	1.97	19700	0.74	1.9	143	33	3	1	0.01	26	0.01	15.0	23	0.01
KL46-04	558.5	561.5	2.23	22300	0.94	2.5	132	175	13	3	0.01	26	0.2	20.0	34	0.01
KL46-04	561.5	564.5	1.14	11400	0.31	1.8	182	173	2	23	1	27	0.7	13.0	32	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL46-04	564.5	567.5	1.78	17800	0.93	5.2	194	60	1	4	8	29	0.3	17.0	33	0.01
KL46-04	567.5	570.5	2.94	29400	1.47	3.4	180	123	1	3	0.01	22	0.2	21.0	37	0.01
KL46-04	570.5	573.5	1.28	12800	0.61	2.1	118	105	6	1	0.01	24	0.6	18.8	87	0.01
KL46-04	573.5	576.5	1.65	16500	0.69	1.8	147	363	2	19	1	20	0.6	8.5	33	0.01
KL46-04	576.5	579.5	2.86	28600	0.89	2.4	148	26	1	4	0.01	31	0.3	14.0	30	0.01
KL46-04	579.5	582.5	0.9	9000	0.47	0.8	162	33	0.01	7	0.01	26	0.5	4.5	21	0.01
KL46-04	582.5	585.5	1.61	16100	0.87	1.7	125	37	0.01	3	0.01	30	0.4	8.5	17	0.01
KL46-04	585.5	588.5	2.95	29500	2.81	3.2	208	27	0.01	91	0.01	31	0.3	7.5	32	0.01
KL46-04	588.5	591.5	2.73	27300	1.07	2.4	336	33	1	4	0.01	60	0.2	20.0	32	0.01
KL46-04	591.5	594.5	1.07	10700	0.53	1.7	302	96	36	3	0.01	22	1.3	9.0	31	0.01
KL46-04	594.5	597.5	2.28	22800	1.21	3.2	540	37	2	11	0.01	63	0.7	13.0	47	0.01
KL46-04	597.5	600.5	2.46	24600	0.92	2.8	192	35	3	198	0.01	96	0.6	11.0	35	0.01
KL46-04	600.5	603.5	1.42	14200	0.52	1.9	316	90	2	41	0.01	84	0.8	4.0	47	0.01
KL46-04	603.5	605.6	2.54	25400	1.25	3.3	560	35	5	8	0.01	59	0.6	16.0	42	0.01
KL46-04	605.6	607.2	2.31	23100	1.33	3.5	530	39	16	108	1	48	0.5	19.0	123	0.01
KL46-04	607.2	609.2	0.72	7200	0.12	1.1	142	44	4	190	0.01	9	0.4	4.5	66	0.01
KL46-04	609.2	610.6	0.95	9500	0.4	1.4	202	25	13	107	0.01	10	0.3	5.8	90	0.01
KL46-04	610.6	612.5	2.33	23300	0.62	7.5	920	62	21	420	0.01	15	1.2	11.0	76	0.01
KL46-04	612.5	615.5	1.46	14600	0.54	3.1	460	30	17	310	0.01	15	0.5	8.5	112	0.01
KL46-04	615.5	618.5	0.075	750	0.08	0.1	43	23	13	16	0.01	2	1.3	1.3	28	0.01
KL46-04	618.5	621.5	0.491	4910	0.18	1.2	187	36	11	91	1	10	0.2	5.5	108	0.01
KL46-04	621.5	624.5	0.72	7200	0.27	1.7	272	72	6	138	1	20	0.2	4.8	109	0.01
KL46-04	624.5	627.5	1.15	11500	0.27	3.2	410	73	11	289	2	16	0.7	5.5	104	0.01
KL46-04	627.5	630.5	0.84	8400	0.18	3.1	278	43	22	127	3	12	2.8	5.0	80	0.01
KL46-04	630.5	633.4	1.24	12400	0.39	3.6	100	26	21	520	6	12	1.3	6.5	124	0.01
KL46-04	633.4	636.5	0.85	8500	0.27	2.6	186	23	8	262	0.01	14	7.5	7.5	116	0.01
KL46-04	636.5	639.5	0.62	6200	0.13	2	147	27	7	420	1	11	1.1	4.5	103	0.01
KL46-04	639.5	642.5	0.465	4650	0.1	1.7	158	45	8	223	1	11	1.4	4.8	79	0.01
KL46-04	642.5	645.5	0.7	7000	0.11	2.4	248	29	17	59	1	10	1.7	4.8	85	0.01
KL46-04	645.5	648.5	1.51	15100	0.5	2.5	440	29	10	196	1	16	0.3	9.0	75	0.01
KL46-04	648.5	651.5	0.483	4830	0.1	1.5	352	263	24	98	5	10	1	5.5	53	0.01
KL46-04	651.5	654.5	1.31	13100	0.48	1.9	380	34	11	170	1	13	0.4	6.0	84	0.01
KL46-04	654.5	657.5	0.82	8200	0.4	2.6	530	166	31	254	5	12	1	4.0	73	0.01
KL46-04	657.5	660.5	0.62	6200	0.35	2.2	396	186	10	241	2	13	0.9	3.3	81	0.01
KL46-04	660.5	663.5	0.9	9000	0.24	3.9	234	38	15	392	2	17	1.8	8.5	99	0.01
KL46-04	663.5	666.5	0.89	8900	0.24	4	240	42	19	219	3	14	2.4	6.0	80	0.01
KL46-04	666.5	669.5	0.48	4800	0.29	2.2	182	23	12	49	2	17	0.4	2.8	103	0.01
KL46-04	669.5	672.5	0.325	3250	0.12	2	109	52	9	112	2	11	1.1	3.0	91	0.01
KL46-04	672.5	675.5	0.22	2200	0.1	2	406	287	43	213	8	8	0.8	8.5	63	0.01
KL46-04	675.5	678.5	0.371	3710	0.1	2.1	186	135	54	114	4	8	0.9	7.8	74	0.01
KL46-04	678.5	681.5	0.359	3590	0.22	2.5	670	111	13	121	8	8	0.6	3.7	77	0.01
KL46-04	681.5	684.5	0.33	3300	0.33	3.4	460	241	17	47	15	10	1	5.3	80	0.01
KL46-04	684.5	685.9	0.393	3930	0.43	1.7	128	51	22	30	14	11	1.6	8.0	90	0.01
KL46-04	685.9	687.5	1.2	12000	0.7	4.7	103	28	20	20	9	12	0.6	17.0	49	0.11
KL46-04	687.5	690.5	0.392	3920	0.13	1.4	151	40	110	82	10	11	3	23.0	34	0.1
KL46-04	690.5	693.5	0.058	580	0.16	0.7	192	63	93	9	10	14	1.8	21.8	26	0.1
KL46-04	693.5	696.5	1.3	13000	0.37	5.7	215	77	64	46	16	17	2.2	28.0	131	0.43
KL46-04	696.5	699.5	2.03	20300	0.56	2.5	207	73	21	64	3	20	0.6	28.0	92	0.19
KL46-04	699.5	702.5	1.02	10200	0.36	2.8	117	42	58	129	1	14	37	11.0	96	0.3
KL46-04	702.5	705.5	0.68	6800	0.1	2.6	135	60	190	25	2	8	46	13.8	224	0.26
KL46-04	705.5	708.5	0.083	830	0.04	1.1	90	64	42	103	1	10	15.8	17.4	42	0.1
KL46-04	708.5	711.5	0.22	2200	0.06	1.1	65	22	14	57	0.01	12	5.7	8.3	80	0.01
KL46-04	711.5	714.5	0.0376	376	0.01	0.7	47	23	15	14	0.01	4	10.8	2.3	212	0.01
KL46-04	714.5	717.5	0.132	1320	0.03	0.9	42	22	46	33	0.01	4	13.2	6.5	262	0.12
KL46-04	717.5	720.5	0.057	570	0.02	0.7	25	20	27	20	1	10	7.3	5.5	180	0.01
KL46-04	720.5	723.5	0.093	930	0.02	1	74	40	33	65	0.01	7	8.2	5.5	233	0.01
KL46-04	723.5	726.5	0.084	840	0.02	0.5	65	29	12	34	0.01	6	2	7.0	117	0.01
KL46-04	726.5	729.5	0.057	570	0.02	1.4	254	100	50	97	1	8	18.8	7.6	161	0.11
KL46-04	729.5	731.7	0.082	820	0.08	9	1210	1040	63	15	0.01	3	38	2.4	161	0.22
KL46-04	731.7	734.8	0.0208	208	0.02	20.7	225	80	17	29	1	5	0.3	6.0	170	0.01
KL46-04	734.8	737.9	0.075	750	0.01	0.5	42	32	10	33	0.01	9	0.7	4.0	228	0.01
KL46-04	737.9	741	0.27	2700	0.04	1.1	77	40	13	60	2	20	1.4	9.8	182	0.01
KL46-04	741	744	0.137	1370	0.02	0.5	55	39	7	25	1	11	0.4	4.5	83	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL46-04	744	747.1	0.356	3560	0.06	1.1	48	32	9	28	3	6	1.8	3.5	113	0.01
KL46-04	747.1	750.2	0.209	2090	0.07	1.1	174	78	200	35	3	10	22.3	9.5	176	0.01
KL46-04	750.2	753.3	0.153	1530	0.03	1	347	161	120	7	3	6	2.2	3.5	137	0.15
KL46-04	753.3	756.4	0.23	2300	0.08	0.7	107	56	7	29	0.01	4	0.2	3.0	162	0.01
KL46-04	756.4	759.5	0.67	6700	0.31	2.1	120	41	23	42	1	7	1	6.5	218	0.01
KL46-04	759.5	762.5	0.275	2750	0.09	1.2	152	68	12	60	1	6	0.6	3.5	250	0.01
KL46-04	762.5	765.5	0.464	4640	0.11	1.7	260	116	32	165	3	20	1.1	7.0	185	0.01
KL46-04	765.5	768.5	0.297	2970	0.08	0.9	52	30	5	41	2	11	0.8	5.8	159	0.01
KL46-04	768.5	771.5	0.22	2200	0.05	1.1	33	17	2	19	1	7	0.4	3.2	174	0.01
KL46-04	771.5	774.5	0.201	2010	0.02	1.5	132	167	28	59	2	7	6.6	3.7	220	0.01
KL46-05	0	2.3	0.0024	24	0.01	0.1	43	32	7	2	0.01	1	0.3	1.5	16	0.01
KL46-05	2.3	5.3	0.0041	41	0.01	0.1	64	18	6	2	0.01	1	0.5	0.7	19	0.01
KL46-05	5.3	8.3	0.0022	22	0.01	0.1	72	16	12	3	0.01	1	0.7	1.2	21	0.01
KL46-05	8.3	11.3	0.0021	21	0.01	0.1	75	26	17	5	0.01	1	0.9	1.5	21	0.01
KL46-05	11.3	14.3	0.0083	83	0.01	0.1	45	10	16	3	0.01	1	0.7	0.7	23	0.01
KL46-05	14.3	17.3	0.0012	12	0.01	0.1	71	82	14	2	0.01	1	0.8	1.7	21	0.1
KL46-05	17.3	20.3	0.0036	36	0.01	0.1	57	29	13	2	0.01	1	1	1.2	16	0.01
KL46-05	20.3	23.3	0.0008	8	0.01	0.1	49	15	7	2	0.01	1	0.7	0.7	27	0.01
KL46-05	23.3	26.3	0.0017	17	0.01	0.1	85	51	4	1	0.01	1	0.5	0.0	15	0.01
KL46-05	26.3	29.3	0.0016	16	0.01	0.1	52	16	4	1	0.01	1	0.6	0.0	17	0.01
KL46-05	29.3	32.3	0.0025	25	0.01	0.1	160	50	11	1	0.01	1	0.9	0.6	24	0.01
KL46-05	32.3	35.3	0.0018	18	0.01	0.1	165	21	4	2	0.01	1	0.7	0.0	13	0.01
KL46-05	35.3	38.3	0.0127	127	0.01	0.1	163	50	14	1	0.01	1	1	0.8	15	0.01
KL46-05	38.3	41.3	0.0137	137	0.01	0.1	297	89	18	1	0.01	1	1.6	1.0	15	0.01
KL46-05	41.3	44.3	0.0013	13	0.01	0.1	120	44	8	1	0.01	1	0.9	0.8	18	0.01
KL46-05	44.3	47.3	0.0017	17	0.01	0.5	239	102	18	1	0.01	1	1.4	1.8	45	0.01
KL46-05	47.3	50.3	0.0034	34	0.01	0.5	540	151	17	1	0.01	1	2.5	0.9	18	0.1
KL46-05	50.3	53.3	0.0017	17	0.01	0.1	80	21	13	1	0.01	1	2	1.5	27	0.01
KL46-05	53.3	55.7	0.001	10	0.01	0.8	64	20	10	1	0.01	1	1.1	1.4	29	0.15
KL46-05	55.7	58.8	0.0046	46	0.01	0.1	177	63	10	10	0.01	1	1.2	1.3	24	0.13
KL46-05	58.8	61.7	0.001	10	0.01	0.1	72	18	16	1	0.01	1	1.1	1.3	23	0.01
KL46-05	61.7	64.2	0.0009	9	0.01	0.1	126	23	20	1	0.01	1	0.8	0.6	25	0.01
KL46-05	64.2	65.3	0.014	140	0.02	2.1	520	93	41	4	0.01	1	2.4	4.1	41	0.53
KL46-05	65.3	68.3	0.0014	14	0.01	1.3	94	30	30	2	0.01	1	1.7	2.0	30	0.34
KL46-05	68.3	71.3	0.0129	129	0.01	0.9	125	47	18	3	0.01	1	1.1	1.4	22	0.18
KL46-05	71.3	74.3	0.0042	42	0.02	0.6	64	16	17	3	0.01	1	0.9	1.3	21	0.15
KL46-05	74.3	77.3	0.0252	252	0.01	0.1	46	35	12	4	0.01	1	1	1.6	29	0.01
KL46-05	77.3	80.3	0.0025	25	0.01	0.1	73	48	16	3	0.01	1	0.9	1.0	17	0.01
KL46-05	80.3	83.3	0.0032	32	0.05	0.1	94	28	26	7	0.01	1	1.9	2.6	26	0.41
KL46-05	83.3	86.3	0.0025	25	0.07	0.1	44	19	14	3	0.01	1	1.1	1.1	23	0.2
KL46-05	86.3	89.3	0.0026	26	0.03	0.1	34	12	15	2	0.01	1	1	1.4	24	0.2
KL46-05	89.3	92.3	0.0031	31	0.04	0.1	43	14	17	4	0.01	1	0.8	0.9	21	0.15
KL46-05	92.3	95.3	0.003	30	0.09	0.7	53	18	23	5	0.01	2	1.3	1.2	23	0.38
KL46-05	95.3	98.3	0.03	300	0.07	0.8	302	46	37	5	0.01	3	2	1.7	22	0.24
KL46-05	98.3	101.3	0.0148	148	0.06	0.7	148	28	35	4	0.01	1	2	1.3	21	0.27
KL46-05	101.3	104.3	0.0042	42	0.02	0.1	37	11	16	2	0.01	1	0.7	0.8	21	0.1
KL46-05	104.3	107.3	0.003	30	0.04	0.1	39	13	11	2	0.01	1	0.8	0.9	21	0.17
KL46-05	107.3	110.3	0.0037	37	0.03	0.1	37	14	15	2	0.01	1	0.7	0.9	22	0.11
KL46-05	110.3	113.3	0.0033	33	0.05	0.1	43	11	19	4	0.01	1	1	0.9	21	0.26
KL46-05	113.3	115.8	0.0153	153	0.03	0.1	59	24	18	7	0.01	1	1	0.8	24	0.13
KL46-05	115.8	118.9	0.0037	37	0.02	0.1	69	29	23	3	0.01	1	0.7	1.0	21	0.15
KL46-05	118.9	122	0.0046	46	0.05	0.1	114	39	13	3	0.01	1	0.9	1.2	21	0.27
KL46-05	122	125.1	0.0034	34	0.01	0.1	30	12	11	2	0.01	1	0.5	0.0	20	0.01
KL46-05	125.1	128.2	0.0041	41	0.04	0.6	55	16	23	2	0.01	1	1.2	1.4	20	0.11
KL46-05	128.2	131.3	0.0041	41	0.02	0.1	69	32	20	3	0.01	1	1	0.9	20	0.1
KL46-05	131.3	133.7	0.0174	174	0.06	2.3	290	38	28	2	0.01	1	1.9	1.7	19	0.25
KL46-05	133.7	136.8	0.008	80	0.05	1.8	202	28	18	2	0.01	1	1.6	1.5	20	0.22
KL46-05	136.8	139.7	0.0024	24	0.03	0.1	62	30	12	3	0.01	1	0.9	0.8	19	0.1
KL46-05	139.7	141.1	0.0027	27	0.04	0.1	54	37	12	3	0.01	1	1.2	0.9	15	0.13
KL46-05	141.1	143.3	0.0035	35	0.03	0.1	76	57	15	2	0.01	1	4.1	0.9	9	0.1
KL46-05	143.3	146.3	0.0108	108	0.03	0.1	83	43	15	3	0.01	1	1.3	1.3	14	0.01
KL46-05	146.3	149.3	0.0008	8	0.02	0.1	88	27	10	1	0.01	1	1	1.5	11	0.01
KL46-05	149.3	152.3	0.0012	12	0.02	0.1	50	16	5	1	0.01	1	0.5	1.2	9	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL46-05	152.3	155.3	0.035		350	0.03	0.6	107	35	13	4	0.01	1	1.2	1.7	19	0.1
KL46-05	155.3	158.3	0.0057		57	0.02	0.1	102	58	23	2	0.01	1	1.1	1.5	18	0.01
KL46-05	158.3	160.9	0.001		10	0.03	0.1	112	26	8	2	0.01	1	0.8	1.3	27	0.1
KL46-05	160.9	163.5	0.0168		168	0.04	4.6	640	440	78	4	1	1	7.6	2.0	18	0.14
KL46-05	163.5	166.6	0.0014		14	0.03	0.7	154	168	13	2	0.01	1	1.4	0.9	28	0.1
KL46-05	166.6	169.7	0.0016		16	0.01	0.7	166	80	13	2	0.01	1	1	1.1	29	0.01
KL46-05	169.7	171.1	0.004		40	0.01	0.6	70	78	10	2	0.01	1	1.8	1.0	17	0.1
KL46-05	171.1	173.3	0.0055		55	0.02	0.7	329	327	23	2	0.01	1	1.7	1.4	29	0.13
KL46-05	173.3	175.5	0.198		1980	0.09	29.4	3350	3400	740	4	36	1	46	3.8	38	1.26
KL46-05	175.5	177.5	0.048		480	0.03	6.3	660	600	170	3	8	1	14	1.7	31	0.38
KL46-05	177.5	179.3	0.0093		93	0.01	1.3	207	120	27	2	1	1	3	0.8	26	0.11
KL46-05	179.3	182.3	0.0013		13	0.03	0.1	232	82	22	5	0.01	1	1	1.5	34	0.31
KL46-05	182.3	185.3	0.0012		12	0.01	0.1	650	149	22	3	0.01	1	1.1	1.8	35	0.18
KL46-05	185.3	188.3	0.0137		137	0.02	0.1	460	77	12	3	0.01	1	0.9	1.2	37	0.17
KL46-05	188.3	191.3	0.0137		137	0.01	0.1	100	40	14	3	0.01	1	0.9	1.3	42	0.1
KL46-05	191.3	194.3	0.008		80	0.01	0.1	137	67	22	4	0.01	1	1.9	1.4	58	0.01
KL46-05	194.3	197.3	0.003		30	0.02	0.1	139	53	20	6	0.01	1	1.3	2.1	48	0.17
KL46-05	197.3	200.3	0.0038		38	0.01	0.1	77	26	12	1	0.01	1	2.4	1.5	27	0.01
KL46-05	200.3	203.3	0.0039		39	0.01	0.1	122	51	9	2	0.01	1	0.9	1.2	30	0.01
KL46-05	203.3	206.3	0.0031		31	0.02	0.1	164	43	10	2	0.01	1	1.1	1.4	87	0.11
KL46-05	206.3	208.9	0.0032		32	0.03	0.1	167	40	12	2	0.01	1	1	1.2	94	0.13
KL46-05	208.9	211.6	0.045		450	0.04	0.1	860	190	41	5	0.01	1	1.9	2.3	40	0.01
KL46-05	211.6	214.2	0.0076		76	0.02	0.1	281	83	7	2	0.01	1	0.6	0.5	42	0.01
KL46-05	214.2	215.7	0.0029		29	0.01	0.1	44	26	11	2	0.01	1	0.9	1.0	54	0.01
KL46-05	215.7	218.3	0.0018		18	0.01	0.7	143	480	17	6	0.01	1	2.3	0.7	15	0.01
KL46-05	218.3	221.3	0.0034		34	0.01	0.1	31	12	4	1	0.01	1	0.5	0.7	25	0.01
KL46-05	221.3	224.3	0.0038		38	0.01	0.1	39	12	2	2	0.01	1	0.3	0.5	30	0.01
KL46-05	224.3	227.3	0.0031		31	0.01	0.1	41	18	10	1	0.01	1	0.8	1.1	26	0.01
KL46-05	227.3	230.3	0.0175		175	0.07	1.1	890	380	40	22	0.01	1	40	2.6	79	0.11
KL46-05	230.3	233.3	0.0027		27	0.01	0.1	123	42	15	3	0.01	1	0.9	1.1	33	0.01
KL46-05	233.3	235.6	0.0339		339	0.12	0.7	600	193	23	4	0.01	4	22	1.7	32	0.22
KL46-05	235.6	238.7	0.021		210	0.02	0.1	460	121	14	3	0.01	2	1.1	0.9	31	0.01
KL46-05	238.7	241.8	0.0073		73	0.01	0.1	600	170	7	2	0.01	2	1.3	0.9	32	0.1
KL46-05	241.8	244.8	0.002		20	0.01	0.1	32	34	15	6	0.01	1	0.7	2.6	23	0.01
KL46-05	244.8	248	0.0011		11	0.01	0.1	51	61	16	5	0.01	1	0.7	1.9	16	0.01
KL46-05	248	251.1	0.0023		23	0.01	0.1	173	254	38	4	0.01	3	1.2	0.8	15	0.01
KL46-05	251.1	253.2	0.0018		18	0.01	0.1	130	104	30	4	1	2	2.2	1.3	17	0.01
KL46-05	253.2	254.6	0.0032		32	0.14	1	378	145	33	3	1	8	2.4	5.0	28	0.01
KL46-05	254.6	257.3	0.0017		17	0.01	0.1	124	88	32	5	1	3	2.1	1.3	16	0.01
KL46-05	257.3	260.3	0.0033		33	0.13	0.1	149	50	10	2	0.01	2	0.8	0.7	37	0.12
KL46-05	260.3	263.3	0.0045		45	0.01	0.6	190	218	35	4	3	4	4.8	1.6	28	0.01
KL46-05	263.3	266.3	0.0031		31	0.01	2	358	420	30	1	3	1	1.7	0.0	18	0.01
KL46-05	266.3	269.3	0.0047		47	0.15	2.1	5200	335	83	3	2	1	5.5	2.8	36	0.72
KL46-05	269.3	272.3	0.011		110	0.06	2.4	1370	290	86	3	2	1	11	3.1	21	0.2
KL46-05	272.3	275.3	0.0177		177	0.09	7.1	8200	4500	60	3	7	1	12.3	8.0	11	0.78
KL46-05	275.3	278.3	0.093		930	0.06	1.3	168	118	14	10	1	1	1.8	2.0	28	0.14
KL46-05	278.3	281.3	0.0018		18	0.04	1.5	520	338	23	2	0.01	1	2.2	1.3	14	0.16
KL46-05	281.3	283.9	0.0012		12	0.03	1	339	302	16	2	0.01	1	1.4	1.3	15	0.01
KL46-05	283.9	287	0.0024		24	0.03	0.9	132	116	12	1	0.01	1	1.6	0.8	19	0.01
KL46-05	287	290.1	0.002		20	0.01	2.1	620	371	20	1	0.01	1	2.2	1.5	24	0.01
KL46-05	290.1	293.1	0.0012		12	0.01	1.4	165	177	16	3	0.01	1	1.7	0.9	34	0.01
KL46-05	293.1	296.2	0.0017		17	0.01	1.4	690	660	22	3	0.01	1	2.3	1.8	21	0.01
KL46-05	296.2	299.3	0.0021		21	0.02	1.5	520	440	24	2	0.01	1	2.3	1.0	21	0.01
KL46-05	299.3	302.3	0.0091		91	0.15	3	2200	1800	52	5	0.01	1	12.8	3.7	18	0.68
KL46-05	302.3	305.3	0.0031		31	1.1	1.7	1290	560	40	1	0.01	1	7	2.3	19	0.37
KL46-05	305.3	308.3	0.002		20	4.7	2.3	1670	420	100	5	0.01	1	3.5	4.9	40	0.59
KL46-05	308.3	311.3	0.0025		25	2.56	2.4	1270	240	76	4	0.01	1	3.3	1.8	31	0.38
KL46-05	311.3	314.3	0.0022		22	0.8	1	800	187	28	1	5	1	1.7	2.4	21	0.41
KL46-05	314.3	317.3	0.0017		17	0.04	0.6	126	65	6	1	0.01	1	0.6	0.5	20	0.1
KL46-05	317.3	320.3	0.0019		19	0.01	0.6	158	68	6	1	0.01	1	0.5	0.0	22	0.01
KL46-05	320.3	323.3	0.0026		26	0.02	1.4	256	157	7	1	0.01	1	5.8	1.0	21	0.01
KL46-05	323.3	326.3	0.0031		31	0.02	0.7	189	128	7	1	0.01	1	15.5	0.7	30	0.13
KL46-05	326.3	329.3	0.002		20	0.02	0.1	246	116	5	3	0.01	1	1.4	1.8	21	0.11

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL46-05	329.3	332.3	0.0011	11	0.01	0.1	115	48	7	2	0.01	1	0.4	0.5	20	0.01
KL46-05	332.3	335.3	0.0019	19	0.01	0.5	175	190	6	1	0.01	1	1.2	0.5	21	0.01
KL46-05	335.3	338.3	0.0011	11	0.01	0.1	176	200	5	1	0.01	1	0.5	0.8	22	0.01
KL46-05	338.3	341.3	0.0008	8	0.01	0.1	48	21	4	1	0.01	1	0.5	0.8	21	0.01
KL46-05	341.3	344.3	0.0176	176	0.1	10.5	8000	12700	85	1	0.01	1	20.5	6.0	25	1.2
KL46-05	344.3	347.3	0.0018	18	0.01	0.1	81	29	4	2	0.01	1	0.2	1.0	23	0.13
KL46-05	347.3	350	0.0014	14	0.01	0.6	61	46	2	1	0.01	1	0.3	1.0	22	0.01
KL46-05	350	353.1	0.0012	12	0.01	0.5	73	33	2	1	0.01	1	0.3	1.5	21	0.01
KL46-05	353.1	356.2	0.0014	14	0.01	0.1	26	25	5	1	0.01	1	0.6	2.0	28	0.01
KL46-05	356.2	359.3	0.0027	27	0.02	0.8	216	254	26	7	2	1	9.2	1.8	16	0.01
KL46-05	359.3	362.3	0.0018	18	0.01	1.1	238	215	27	3	1	1	1.4	1.0	46	0.01
KL46-05	362.3	365.3	0.0018	18	0.01	0.7	113	82	18	2	1	1	1	1.0	34	0.01
KL46-05	365.3	368.3	0.0026	26	0.2	2	259	125	95	3	2	1	3	5.5	31	0.15
KL46-05	368.3	371.3	0.008	80	0.03	0.9	630	270	32	5	1	1	9.8	3.5	27	0.01
KL46-05	371.3	374.3	0.003	30	0.08	1.2	416	165	30	3	0.01	1	3	6.0	31	0.15
KL46-05	374.3	377.3	0.0021	21	0.05	0.5	160	91	17	1	0.01	1	3.8	1.5	24	0.01
KL46-05	377.3	380.3	0.0229	229	1.33	15.6	1870	14800	92	1	36	1	40	74.8	40	1.28
KL46-05	380.3	383.3	0.0043	43	0.02	0.1	126	130	16	1	5	1	1.2	9.8	25	0.01
KL46-05	383.3	386.3	0.108	1080	0.18	3.5	346	530	110	6	48	5	8.8	9.5	69	0.01
KL46-05	386.3	389.3	0.043	430	2.37	1	215	161	24	2	1	4	3	5.0	135	0.16
KL46-05	389.3	392.3	0.0156	156	0.09	1.1	115	58	70	1	6	6	4.5	5.3	73	0.16
KL46-05	392.3	395.3	0.0187	187	0.2	1.3	415	369	72	1	0.01	3	5	3.3	135	0.17
KL46-05	395.3	398.3	0.32	3200	0.64	86	21400	30100	1300	8	11	2	180	20.7	37	5.26
KL46-05	398.3	400.9	0.0024	24	1.43	0.1	19	88	19	1	0.01	3	1.4	4.9	202	0.11
KL46-05	400.9	404.1	0.0038	38	0.01	0.6	113	154	55	2	1	3	1.7	0.8	42	0.01
KL46-05	404.1	407	0.0023	23	0.22	0.7	113	52	26	4	1	6	0.8	5.3	73	0.01
KL46-05	407	408.1	0.05	500	0.46	29.5	22500	15200	160	4	2	4	38	45.5	67	2.84
KL46-05	408.1	410.1	0.51	5100	1.7	282	215000	238000	1860	17	5	1	408	60.5	26	40.6
KL46-05	410.1	412.8	1.56	15600	2.86	460	103000	137000	5100	20	58	3	730	66.0	50	21.4
KL46-05	412.8	415.3	0.32	3200	1.34	136	110000	85000	1170	21	10	4	240	87.3	145	20.4
KL46-05	415.3	417.7	0.0076	76	0.09	0.6	1040	290	14	1	1	1	10.8	4.0	32	0.26
KL46-05	417.7	420.2	0.129	1290	0.64	34.7	33600	20500	410	72	3	9	130	39.0	265	3.82
KL46-05	420.2	422.3	0.22	2200	0.53	18.1	9300	5500	270	116	2	5	92	20.5	266	1.22
KL46-05	422.3	426.8	0.0253	253	0.12	4.7	1610	820	47	27	3	4	15.2	5.0	254	0.25
KL46-05	426.8	428.3	0.085	850	0.07	42	16000	8700	240	12	68	4	56	11.5	273	1.96
KL46-05	428.3	429.9	0.31	3100	0.13	91	8100	8500	1240	8	102	4	174	11.0	231	1.84
KL46-05	429.9	432.8	0.0175	175	0.02	3.3	720	480	40	5	5	3	13	1.0	217	0.01
KL46-05	432.8	435.6	0.084	840	0.03	5.9	1560	1050	200	14	6	2	96	3.5	172	0.32
KL46-05	435.6	437.7	0.0215	215	0.09	1.1	680	212	46	12	0.01	2	36	4.3	346	0.1
KL46-05	437.7	439.4	0.0204	204	0.25	4.1	7900	3100	54	36	4	1	40	10.8	107	0.8
KL46-05	439.4	442.7	0.0066	66	0.09	2	1900	920	30	132	1	3	10.8	5.0	147	0.27
KL46-05	442.7	446.3	0.0136	136	0.05	2.8	3000	1700	36	6	4	1	16.7	4.3	308	0.35
KL46-05	446.3	449	0.194	1940	0.31	8.2	5500	2500	190	16	14	1	282	13.0	306	0.64
KL46-05	449	451.4	0.22	2200	0.15	14.2	6000	3200	180	101	24	1	1090	9.3	200	1.04
KL46-05	451.4	454.3	1.4	14000	0.46	24.2	4700	6500	780	164	7	2	4870	8.5	290	1.2
KL46-05	454.3	457.4	0.41	4100	0.57	35.1	2500	3800	270	335	6	3	2400	6.3	195	0.68
KL46-05	457.4	460.5	0.078	780	0.11	7.9	10800	4900	200	379	5	1	284	14.0	58	0.8
KL46-05	460.5	461.9	0.15	1500	0.08	4.5	12100	4500	120	404	4	1	692	18.0	95	0.78
KL46-05	461.9	464	0.16	1600	0.16	6.9	8800	3900	150	508	5	1	682	14.3	108	0.76
KL46-05	464	467.3	0.054	540	0.15	6.5	5600	2300	70	200	6	1	212	9.5	96	0.49
KL46-05	467.3	470.3	0.075	750	0.41	6.9	6800	2600	100	151	4	1	266	7.8	108	0.66
KL46-05	470.3	473.3	0.29	2900	0.32	28	15100	5600	450	46	32	1	890	18.0	345	1.5
KL46-05	473.3	476.3	0.05	500	0.35	17.1	14800	6400	170	105	7	1	80	15.2	189	1.1
KL46-05	476.3	479.3	0.102	1020	0.46	37	10000	4700	350	265	56	5	238	22.5	42	1.26
KL46-05	479.3	482.3	0.47	4700	0.84	16.5	8600	1520	1680	15	3	7	352	24.9	39	1.74
KL46-05	482.3	485.3	0.036	360	1.06	12.9	43700	1900	340	14	10	1	40	35.5	29	7.5
KL46-05	485.3	488.3	0.067	670	0.38	8.4	8900	1000	180	7	8	1	62	13.0	28	2.14
KL46-05	488.3	490.8	0.072	720	0.25	6.7	5900	1050	110	37	5	1	244	10.3	47	1.14
KL46-05	490.8	493.8	0.0019	19	0.03	0.1	116	32	7	2	0.01	1	0.8	1.0	31	0.01
KL46-05	493.8	496.8	0.0026	26	0.03	0.1	93	29	4	1	0.01	1	0.3	1.3	28	0.01
KL46-05	496.8	499.8	0.0362	362	0.4	5.3	12800	3400	170	16	3	1	30	31.3	47	1.7
KL46-05	499.8	501.7	0.147	1470	1.18	20.8	51100	10500	800	37	36	3	170	66.3	43	5.28
KL46-05	501.7	503.3	0.101	1010	1.14	28.8	73000	15200	720	35	36	3	100	65.8	50	6.86

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg	
KL46-05	503.3	505.5	0.52		5200	1.16	186	86500	53000	1950	39	276	3	200	70.0	77	7.74
KL46-05	505.5	508.5	0.094		940	0.26	31.1	24600	10100	410	7	54	1	48	30.2	31	1.7
KL46-05	508.5	511.6	0.042		420	0.17	13.1	12100	4000	160	4	26	1	27	20.5	28	0.84
KL46-05	511.6	514.7	0.0132		132	0.08	3.2	4600	1400	57	12	4	1	20	8.8	31	0.28
KL46-05	514.7	517.4	0.0065		65	0.06	0.7	2200	361	20	1	1	1	9.6	6.3	27	0.21
KL46-05	517.4	520.5	0.0065		65	0.04	0.1	860	225	18	2	0.01	1	7.8	2.4	30	0.11
KL46-05	520.5	523.6	0.054		540	0.13	38	18000	26000	170	9	4	9	54	15.7	211	2.96
KL46-05	523.6	526.7	0.075		750	0.42	1.8	2900	1100	110	4	2	5	32	10.8	25	1.14
KL46-05	526.7	529.8	0.058		580	0.6	4.1	6300	1340	250	18	4	1	80	25.3	39	1.48
KL46-05	529.8	532.9	0.0039		39	0.14	1.8	650	296	21	4	1	1	11.5	6.8	35	0.31
KL46-05	532.9	536	0.0069		69	0.23	3.4	280	200	71	6	3	3	2.5	4.7	98	0.01
KL46-05	536	539.1	0.0126		126	0.11	1.8	4120	1760	22	6	1	1	30	8.8	28	0.54
KL46-05	539.1	541.2	0.0034		34	0.15	1	1810	360	21	5	1	1	7	6.8	17	0.36
KL46-05	541.2	542.7	0.0047		47	0.09	0.1	680	480	7	9	0.01	1	7.7	6.5	15	0.17
KL46-05	542.7	545.3	0.0066		66	0.06	0.8	590	570	15	13	2	1	10.6	7.0	13	0.17
KL46-05	545.3	547.4	0.0126		126	0.09	1.1	1050	1250	36	11	2	1	19.8	13.3	14	0.58
KL46-05	547.4	549	0.0041		41	0.06	0.1	231	100	9	11	1	2	4.6	3.2	10	0.1
KL46-05	549	551.2	0.0055		55	0.04	0.8	378	330	9	9	3	1	3.2	8.0	12	0.1
KL46-05	551.2	553.6	0.0213		213	0.32	0.8	1940	470	73	29	3	2	14	15.5	26	0.8
KL46-05	553.6	555.8	0.0189		189	1.24	0.6	690	363	120	11	3	1	24	18.8	20	0.66
KL46-05	555.8	557.3	0.0091		91	0.25	2.4	2000	2120	70	4	2	8	15.4	17.0	15	0.52
KL46-05	557.3	560.3	0.0182		182	1.34	1.7	1310	580	560	1	0.01	18	46	6.9	60	3.16
KL46-05	560.3	563.3	0.303		3030	0.83	3.4	4480	2120	250	6	6	15	60	13.3	26	1.58
KL46-05	563.3	565.4	0.0164		164	0.14	5.4	1630	8900	21	6	2	1	14.8	27.4	15	0.14
KL46-05	565.4	568.5	0.0202		202	0.06	0.7	315	460	20	5	1	1	5.6	9.3	19	0.01
KL46-05	568.5	571.6	0.0182		182	0.03	1.4	4080	4400	26	5	0.01	1	7.5	39.4	14	0.13
KL46-05	571.6	574.7	0.015		150	0.08	0.8	590	325	33	3	1	1	24	5.0	13	0.01
KL46-05	574.7	576.9	0.0155		155	0.21	4	7000	4300	37	6	0.01	1	15.2	6.8	16	0.27
KL46-05	576.9	578.3	0.29		2900	0.42	27.9	23100	33200	870	8	0.01	1	140	6.5	14	0.68
KL46-05	578.3	581.3	0.0261		261	0.11	2.3	1150	820	32	6	1	1	46	8.3	11	0.1
KL46-05	581.3	584.3	0.65		6500	0.4	16.1	7100	3800	180	35	8	11	35	38.5	28	0.13
KL46-05	584.3	586.3	0.317		3170	0.36	11.9	3680	2080	120	31	10	10	27	23.8	23	0.1
KL46-05	586.3	589.4	0.206		2060	0.18	6.9	4310	2220	60	22	9	3	65	42.8	20	0.1
KL46-05	589.4	592.5	0.061		610	0.07	3.2	1400	1150	58	10	5	1	72	25.0	17	0.01
KL46-05	592.5	595.6	5.89		58900	1.21	89	23300	14700	1470	12	103	12	300	27.5	23	1.48
KL46-05	595.6	598.6	0.148		1480	0.17	3.5	3450	1740	310	15	5	6	47	15.8	18	0.15
KL46-05	598.6	601.7	1.97		19700	0.48	45	10900	69500	400	8	9	3	150	53.0	16	0.56
KL46-05	601.7	604.7	0.0373		373	0.08	0.9	1050	410	35	10	1	1	6.7	12.0	14	0.01
KL46-05	604.7	607.8	0.068		680	0.05	0.6	296	95	24	7	1	3	3.2	4.2	25	0.01
KL46-05	607.8	610.9	0.0256		256	0.04	0.5	780	94	46	7	6	1	3.4	5.2	13	0.01
KL46-05	610.9	614	0.178		1780	0.26	1.8	1750	353	68	10	1	9	15.2	10.5	19	0.18
KL46-05	614	617.1	0.051		510	0.26	0.8	980	230	58	6	2	3	5	6.0	23	0.01
KL46-05	617.1	620.2	0.168		1680	0.34	9.5	930	335	140	9	2	2	122	11.8	21	0.01
KL46-05	620.2	623.3	0.073		730	0.08	4.7	223	118	33	60	3	1	30	8.5	13	0.01
KL46-05	623.3	626.3	0.063		630	0.11	1.2	1310	131	22	10	3	2	3.1	6.5	12	0.01
KL46-05	626.3	629.3	0.061		610	0.07	1.5	660	490	30	6	6	3	7.4	13.8	27	0.01
KL46-05	629.3	632.3	0.32		3200	0.22	1.3	172	47	12	13	2	4	2.7	6.5	21	0.01
KL46-05	632.3	635.3	0.135		1350	0.03	11	119	308	39	239	78	6	5.2	16.2	59	0.01
KL46-05	635.3	638.3	0.56		5600	0.12	27.9	2850	2260	95	146	14	23	4.3	22.6	79	0.01
KL46-05	638.3	641.3	0.416		4160	0.25	1.6	231	45	13	10	2	6	1.1	6.5	20	0.01
KL46-05	641.3	643.9	1.95		19500	0.6	3.9	430	47	16	101	3	31	3.6	7.5	30	0.01
KL46-05	643.9	647	2.84		28400	0.96	6.5	530	62	11	36	8	45	5.9	13.0	37	0.1
KL46-05	647	651	3.14		31400	0.96	6.6	420	27	17	30	7	62	5.5	9.0	53	0.01
KL46-05	651	653.1	0.66		6600	0.41	9.5	18500	6000	290	23	1	20	17.8	13.5	74	0.27
KL46-05	653.1	656.2	0.297		2970	0.19	1.1	2250	157	170	21	1	12	6.5	4.8	41	0.01
KL46-05	656.2	659.3	0.124		1240	0.05	0.1	55	26	4	113	0.01	2	1.2	1.8	110	0.01
KL46-05	659.3	662.3	0.433		4330	0.23	0.8	106	27	2	13	0.01	8	0.4	5.3	63	0.01
KL46-05	662.3	665.3	0.191		1910	0.14	1	113	46	8	112	0.01	4	1.3	1.3	65	0.01
KL46-05	665.3	668.3	0.174		1740	0.09	1.7	4860	880	140	20	1	10	6.3	6.5	64	0.01
KL46-05	668.3	671.3	0.26		2600	0.08	1.8	790	156	6	152	3	3	1.7	7.0	67	0.01
KL46-05	671.3	674	0.23		2300	0.12	0.1	60	26	1	73	0.01	3	0.5	2.4	84	0.01
KL46-05	674	677.1	1.09		10900	0.62	1.1	215	32	7	10	1	8	2.8	8.5	30	0.01
KL46-05	677.1	680.2	0.263		2630	0.09	3	2990	1520	29	129	3	6	3	5.2	187	0.01

Hole	From	To	Cu		Au	Ag	Zn	Pb	As	Mo	Bi	Co	Sb	Se	Cr	Hg
KL46-05	680.2	683.3	0.23	2300	0.1	1.5	346	72	9	111	1	5	1.8	3.8	64	0.01
KL46-05	683.3	685.9	0.216	2160	0.09	0.1	96	24	5	120	0.01	3	0.9	3.3	58	0.01
KL46-05	685.9	689	0.183	1830	0.08	1.4	3000	880	64	72	0.01	5	3.2	4.5	65	0.01
KL46-05	689	690.3	0.31	3100	0.13	0.8	840	254	23	38	1	9	2.3	4.8	50	0.01
KL46-05	690.3	692.3	0.206	2060	0.11	1	980	282	17	191	0.01	5	1.8	5.1	114	0.01
KL46-05	692.3	695.3	0.194	1940	0.07	0.9	79	23	6	54	1	4	1	0.5	51	0.01
KL46-05	695.3	698.3	0.25	2500	0.15	0.1	164	23	16	22	0.01	7	4.2	3.3	48	0.01
KL46-05	698.3	701.3	0.31	3100	0.13	0.8	181	34	10	37	1	8	1.4	3.5	84	0.01
KL46-05	701.3	704.3	0.29	2900	0.14	0.7	330	75	12	57	1	7	1.5	3.8	91	0.01
KL46-05	704.3	707.3	0.24	2400	0.14	0.6	252	32	9	12	0.01	6	1.4	2.8	27	0.01
KL46-05	707.3	710.3	0.211	2110	0.12	0.1	269	258	3	5	0.01	8	1.1	3.8	39	0.01
KL46-05	710.3	713.3	0.408	4080	0.26	1.1	420	49	10	43	2	10	1.9	5.0	39	0.01
KL46-05	713.3	716.3	0.8	8000	0.51	3.6	700	550	25	14	2	18	7.6	5.8	62	0.24
KL46-05	716.3	719.3	0.47	4700	0.28	0.8	273	120	10	36	1	8	1.6	4.0	43	0.01
KL46-05	719.3	722.3	0.26	2600	0.24	0.7	75	19	13	34	1	5	4.3	3.3	46	0.01
KL46-05	722.3	724.7	0.31	3100	0.51	1.3	470	60	13	26	4	6	3.2	4.5	107	0.01
KL46-05	724.7	726.9	0.37	3700	0.2	1.2	10000	272	83	25	0.01	18	2.7	3.3	108	0.01
KL46-05	726.9	728.3	0.212	2120	0.12	1.8	4910	870	240	33	1	13	6.7	3.3	66	0.1
KL46-05	728.3	731.3	0.3	3000	0.2	1.1	1160	283	60	43	3	8	4.5	4.5	118	0.01
KL46-05	731.3	734.3	0.53	5300	0.22	1.4	4620	890	10	7	3	14	2.8	5.4	133	0.01
KL46-05	734.3	737.3	0.3	3000	0.18	1	550	102	15	15	3	9	4.6	3.5	61	0.01
KL46-05	737.3	740.3	0.405	4050	0.21	1.5	1230	820	12	6	0.01	12	4.3	5.0	20	0.22
KL46-05	740.3	743.3	0.24	2400	0.1	0.7	8700	1800	7	10	2	11	2.2	3.0	113	0.01
KL46-05	743.3	746.3	1.11	11100	0.82	2.7	22600	7200	54	11	4	18	5.6	11.5	84	0.01
KL46-05	746.3	749.3	0.92	9200	0.52	2.2	36400	8200	330	69	2	14	5.3	13.5	45	0.1
KL46-05	749.3	752.3	0.4	4000	0.2	1.2	37600	5600	26	59	1	13	5	4.5	33	0.01
KL46-05	752.3	755.3	1.31	13100	0.46	1.1	3600	1470	2	43	1	27	0.2	19.0	26	0.01
KL46-05	755.3	758.3	1.41	14100	0.34	3	10000	2100	8	48	1	21	1	14.5	54	0.01
KL46-05	758.3	761.3	1.25	12500	0.44	1.1	1880	302	1	13	0.01	23	0.4	15.0	22	0.01
KL46-05	761.3	764.3	1.9	19000	0.85	3	1210	159	6	11	1	21	0.9	16.8	22	0.01
KL46-05	764.3	767.3	1.2	12000	0.65	4.6	1140	266	8	9	1	22	9.5	13.0	26	0.01
KL46-05	767.3	770.3	2.18	21800	0.85	4.2	272	40	5	19	0.01	26	2.8	25.0	22	0.01
KL46-05	770.3	773.3	0.625	6250	0.44	1.5	281	117	3	13	1	22	0.01	6.5	23	0.01
KL46-05	773.3	776.3	1.56	15600	0.76	2	194	18	2	4	0.01	30	0.3	9.9	16	0.01
KL46-05	776.3	779.3	1.12	11200	0.98	2.2	430	130	4	10	1	30	0.7	9.3	31	0.01
KL46-05	779.3	782.3	1.23	12300	0.8	2.1	168	57	2	40	1	29	0.3	13.0	22	0.01
KL46-05	782.3	785.3	1.55	15500	0.86	2.9	163	23	3	4	0.01	24	0.5	9.3	23	0.01
KL46-05	785.3	788.4	1.29	12900	0.76	1.7	147	25	3	17	0.01	17	0.4	11.5	37	0.01
KL46-05	788.4	791.3	2.53	25300	1.54	4.3	183	15	2	8	0.01	21	0.01	20.0	30	0.01
KL46-05	791.3	794.3	1.89	18900	1.28	2.2	157	16	2	1	0.01	35	0.3	14.0	17	0.01
KL46-05	794.3	797	1.53	15300	1.2	2.3	216	22	2	6	0.01	35	0.6	9.0	20	0.01
KL46-05	797	800.1	0.489	4890	0.46	1.2	420	153	2	2	0.01	25	0.7	3.8	19	0.01
KL46-05	800.1	803.1	1.8	18000	1.4	3	328	42	3	5	0.01	34	0.3	14.0	20	0.01
KL46-05	803.1	806.2	1.5	15000	1.35	13.2	1710	710	16	3	7	28	4	12.5	19	0.01
KL46-05	806.2	809.1	0.82	8200	1.35	18.3	2600	3800	40	5	8	26	6.2	47.0	100	0.68
KL46-05	809.1	812	1.03	10300	0.66	11.3	620	278	28	1	13	40	6.2	31.0	108	0.98
KL46-05	812	815.1	1.12	11200	0.7	12.6	670	300	24	1	18	37	5.9	53.0	109	1.1
KL46-05	815.1	818.2	1.86	18600	1.49	2.5	194	35	3	1	5	24	1.2	12.0	32	0.1
KL46-05	818.2	820.5	1.26	12600	0.97	9.3	2100	2730	26	3	3	22	26	9.8	52	0.72
KL46-05	820.5	822.3	0.271	2710	0.39	2	1310	540	35	16	3	24	3	6.0	67	0.39
KL46-05	822.3	825.3	0.55	5500	0.54	1.3	214	40	8	23	1	13	1.3	6.5	58	0.01
KL46-05	825.3	827.1	0.501	5010	0.4	1.3	181	31	9	26	1	10	1.3	5.3	60	0.01

Appendix VI – Fluid inclusion analysis

EXPERIMENTAL RESULTS

Table VI-1 Results of thermometric experiments

Hole	metre	comp	type	T_e	T_{hh}	T_{ice}	T_{syl}	T_{hal}	T_{vap}	Ph	ice
KL32-1	263.8	SLV	P						670.0	*	Br
KL32-1	263.8	SLV	P					371.4	670.0	*	Br
KL32-5	376.4	VL	PS			-9.0			670.0	*	
KL32-5	376.4	SLV	P					398.6	670.0	*	
KL32-5	376.4	SLV	P					418.7	670.0	*	
KL32-5	376.4	SLV	P					415.6	670.0	*	
KL32-5	376.4	SLV	P					410.7	670.0	*	
KL32-5	376.4	SLV	P					428.7	670.0	*	
KL32-5	376.4	SLV	P				107.9	319.2	670.0	*	
KL32-5	376.4	SLV	P					314.0	665.7	L	
KL32-5	339.2	SLV	P					391.7	650.0	**	
KL32-5	339.2	SLV	P					403.0	650.0	*	
KL32-5	339.2	SLV	P					404.0	650.0	*	
KL32-5	339.2	SLV	P					401.0	650.0	*	
KL32-5	339.2	SLV	P					390.0	650.0	*	
KL32-5	376.4	SLV	P			-5.2	83.5	316.6	612.1	L	
KL32-5	706.7	VL	PS						600.0	*	
KL32-5	706.7	VL	PS						600.0	*	
KL32-5	706.7	VL	PS						600.0	*	
KL32-5	706.7	VL	PS						600.0	*	
KL32-5	376.4	SLV	P					278.0	595.8	L	
KL32-5	706.7	VL	PS						580.0	V	
KL32-5	376.4	SLV	P					376.4	550.0	L	
KL32-5	706.7	VL	S						539.2	V	
KL32-5	706.7	LV	PS	-26.5	26.5	-19.0			520.0	L	Br
KL32-5	706.7	VL	PS	-35.4		-7.8			520.0	V	
KL32-5	706.7	LV	PS	-46.0		-15.0			500.0	L	
KL32-5	706.7	VL	PS						460.0	V	
KL38-5	225.4	SLV	P					314.1	454.5	L	
KL32-5	706.7	VL	S		-32.2	-22.3			451.2	V	
KL48-1	100.2	SLV	PS				225.7	410.1	443.5	L	
KL32-1	263.8	LV	PS		-34.0	-27.0			437.0	L	Br

Hole	metre	comp	type	T _e	T _{hh}	T _{ice}	T _{syl}	T _{hal}	T _{vap}	Ph	ice
KL32-5	706.7	VL	PS						435.0	V	
KL48-1	100.2	SLV	P		10.7		186.4	426.3	431.7	L	Br
KL32-5	706.7	LV	S		15.0	-25.0			429.0	L	
KL32-5	706.7	VL	PS						427.0	V	
KL48-1	100.2	LV	PS	-48.8	-26.2	-13.8			422.7	L	Br
KL48-1	100.2	SLV	P	-53.0		19.7	52.1	132.1	422.7	L	Br
KL32-5	376.4	VL	PS						421.7	L	
KL32-1	263.8	LV	PS			-26.4			416.9	L	Br
KL48-1	100.2	SLV	P	-53.0	-26.2	-1.8	54.4	130.6	416.7	L	Br
KL32-1	263.8	LV	PS		-33.0	-28.4			416.2	L	Br
KL48-1	100.2	LV	PS	-47.5		-12.0			415.8	L	Br
KL48-1	100.2	SLV	P	-53.0			74.8	128.6	415.8	L	Br
KL32-1	263.8	LV	PS	-47.0		-25.2			415.5	L	Br
KL48-1	100.2	SLV	P	-53.0			54.4	128.0	415.0	L	Br
KL32-1	263.8	SLV	P					375.0	413.1	L	Br
KL48-1	100.2	SLV	P	-53.0	-14.6	22.3	53.8	127.1	413.1	L	Br
KL48-1	100.2	SLV	P	-53.0		-1.8	52.1	131.4	413.0	L	Br
KL32-1	263.8	LV	PS			-26.4			408.2	L	Br
KL38-5	225.4	SLV	P				135.6	400.1	407.8	L	
KL48-1	100.2	SLV	P	-53.0		26.2	54.4	128.6	406.5	L	Br
KL48-1	100.2	SLV	P	-53.0			52.1	132.4	406.0	L	Br
KL32-3	354.3	SLV	P				149.5	323.0	405.0	L	
KL48-1	100.2	SLV	PS						402.0	L	Br
KL38-5	225.4	SLV	P					392.4	401.0	L	
KL48-1	100.2	LV	PS						398.9	L	Br
KL48-1	100.2	SLV	P		13.2			209.2	392.3	L	Br
KL32-1	263.8	SLV	P				113.0	395.0	391.5	L	Br
KL48-1	100.2	LV	PS			-11.0			387.0	L	Br
KL32-1	263.8	SLV	P	-47.3	-29.6		104.0	371.4	385.5	L	Br
KL32-1	263.8	SLV	P					386.0	385.3	L	Br
KL48-1	100.2	SLV	P	-53.0			57.0	125.2	384.6	L	Br
KL32-3	354.3	VL	PS						383.0	V	
KL32-3	354.3	VL	PS			-4.9			383.0	V	
KL32-5	376.4	VL	PS			-2.0			379.5	L	
KL48-1	100.2	LV	PS	-45.0		-14.5			376.9	L	Br
KL48-1	100.2	LV	PS						375.3	L	Br
KL32-5	376.4	VL	PS			-9.5			375.0	L	
KL48-1	100.2	LV	PS						369.1	L	Br

Hole	metre	comp	type	T _e	T _{hh}	T _{ice}	T _{syl}	T _{hal}	T _{vap}	Ph	ice
KL32-5	706.7	LV	S						368.0	L	
KL48-1	100.2	LV	PS			-11.9			367.5	L	Br
KL38-5	225.4	SLV	P					360.0	367.1	L	
KL38-5	225.4	SLV	P				132.3	370.0	367.0	L	
KL32-1	263.8	SLV	P	-48.0			105.8		366.8	L	Br
KL32-1	263.8	LV	PS			-19.3			366.3	L	Br
KL32-5	706.7	VL	PS						365.0	V	
KL38-5	225.4	SLV	P					370.0	364.0	L	
KL32-5	706.7	LV	PS						362.3	L	
KL32-1	263.8	SLV	P				122.0	399.5	360.2	L	Br
KL48-1	100.2	SLV	P	-53.0	-34.0	-0.8	100.9	277.8	358.3	L	
KL32-1	263.8	SLV	P				134.0	345.0	355.6	L	Br
KL48-1	100.2	LV	PS						355.6	L	Br
KL32-3	354.3	SLV	P					423.6	354.6	L	Br
KL32-1	263.8	LV	PS		50.0	-20.0			354.2	L	Br
KL38-5	225.4	SLV	P				125.0	345.0	353.3	L	
KL32-1	255.7	LV	PS			-5.0			352.9	L	
KL32-1	263.8	SLV	P				130.0	399.7	352.3	L	Br
KL32-5	706.7	LV	PS		18.2				352.2	L	
KL48-1	100.2	LV	PS						351.8	L	Br
KL32-1	263.8	LV	PS		46.0	-24.4			351.4	L	Br
KL32-3	354.3	SLV	P						350.0	L	
KL48-1	100.2	LV	PS						344.4	L	Br
KL48-1	100.2	LV	PS						344.1	L	Br
KL48-1	100.2	LV	PS			-11.5			343.6	L	Br
KL32-3	354.3	SLV	P				110.5	393.8	338.9	L	Br
KL32-1	263.8	LV	PS						338.8	L	
KL32-3	354.3	LV	S						338.5	L	
KL32-5	706.7	LV	PS			-4.7			338.3	L	
KL32-5	706.7	SLV	P						334.9	L	
KL48-1	100.2	LV	S						331.6	L	
KL32-1	263.8	LV	PS			-23.0			331.4	L	Br
KL48-1	100.2	LV	S			-3.3			331.4	L	
KL48-1	100.2	LV	S						328.6	L	
KL32-3	354.3	LV	S						328.0	L	
KL32-3	354.3	SLV	P				112.3	340.2	327.7	L	Br
KL48-1	100.2	LV	S						327.0	L	
KL48-1	100.2	LV	S						326.7	L	

Hole	metre	comp	type	T _e	T _{hh}	T _{ice}	T _{syl}	T _{hal}	T _{vap}	Ph	ice
KL32-5	706.7	VL	PS						326.0	V	
KL48-1	100.2	LV	S			-2.0			325.8	L	
KL48-1	100.2	SLV	P						325.0	L	
KL32-5	706.7	LV	PS			-22.5			323.1	L	
KL32-5	706.7	LV	PS						320.4	L	
KL32-1	263.8	LV	S						320.0	L	
KL32-5	339.2	SLV	P	-53.3			89.2	154.2	319.5	L	Br
KL32-5	339.2	SLV	P				35.6		318.9	L	Br
KL32-3	354.3	LV	S			-1.2			318.1	L	
KL32-3	354.3	LV	S						317.9	L	
KL32-1	263.8	LV	PS						317.8	L	
KL32-5	706.7	SLV	P					311.5	316.8	L	Br
KL32-1	263.8	LV	PS			-17.6			315.2	L	
KL32-1	263.8	SLV	P				120.0	416.3	315.0	L	Br
KL32-1	263.8	LV	PS			-27.0			314.9	L	
KL32-3	354.3	LV	PS						314.3	L	
KL48-1	100.2	SLV	P				86.4		314.0	L	
KL32-1	263.8	LV	PS			-4.0			313.2	L	
KL32-5	339.2	LV	S						311.9	L	
KL32-5	376.4	LV	PS			-9.5			311.0	L	
KL32-5	706.7	SLV	P				248.2	350.8	310.2	L	Br
KL32-5	706.7	SLV	P					327.2	309.0	L	Br
KL32-3	354.3	LV	S						307.6	L	
KL32-5	706.7	LV	PS						307.2	L	
KL32-1	255.7	LV	PS			-2.3			307.0	L	
KL32-1	255.7	LV	PS			-2.4			304.3	L	
KL32-1	255.7	LV	PS			-2.5			303.5	L	
KL32-5	706.7	LV	PS			-2.5			303.2	L	
KL32-3	354.3	LV	PS						302.5	L	
KL32-5	706.7	SLV	P					357.1	302.5	L	
KL32-3	354.3	LV	PS						302.4	L	
KL32-5	339.2	LV	S	-37.0		-26.4			301.1	L	Br
KL32-1	255.7	LV	PS			-1.8			300.6	L	
KL32-5	339.2	LV	S	-38.0		-26.4			299.0	L	Br
KL32-5	706.7	SLV	P	-52.3				368.7	298.0	L	Br
KL32-5	376.4	SLV	P					270.0	296.5	L	
KL32-1	263.8	SLV	P				125.0	405.6	295.7	L	Br
KL32-5	339.2	LV	S						295.6	L	

Hole	metre	comp	type	T_e	T_{hh}	T_{ice}	T_{syl}	T_{hal}	T_{vap}	Ph	ice
KL32-1	263.8	SLV	P				99.0	409.5	294.3	L	Br
KL32-5	706.7	SLV	P				82.5	305.3	293.2	L	Br
KL32-5	376.4	SLV	P						292.6	L	
KL32-5	339.2	VL	PS						292.3	V	
KL32-3	354.3	LV	PS			-1.5			289.9	L	
KL32-1	255.7	LV	PS			-9.3			288.6	L	Br
KL32-1	255.7	LV	PS			-2.0			288.0	L	
KL32-1	255.7	LV	PS			-2.3			287.7	L	
KL32-1	255.7	LV	PS			-4.2			286.2	L	
KL32-5	706.7	SLV	P					285.1	286.0	L	
KL32-5	706.7	LV	S						285.0	L	
KL32-5	706.7	LV	S						284.3	L	
KL48-1	100.2	SLV	P				181.3	367.1	283.2	L	Br
KL32-5	706.7	SLV	P					371.8	283.1	L	Br
KL32-1	255.7	LV	PS			-2.0			283.0	L	
KL32-5	706.7	LV	S		20.0				281.0	L	
KL32-5	706.7	SLV	P				136.5	444.4	280.3	L	
KL32-5	706.7	VL	PS						280.0	V	
KL32-1	255.7	LV	PS		-28.1	-14.2			275.6	L	Br
KL32-1	255.7	LV	PS						273.0	L	
KL32-1	263.8	SLV	P					412.0	272.0	L	Br
KL48-1	100.2	SLV	P				136.0	385.0	270.0	L	Br
KL48-1	100.2	SLV	P				172.7	392.9	268.6	L	Br
KL48-1	100.2	SLV	P				132.0	390.0	264.5	L	Br
KL32-1	255.7	LV	PS						263.4	L	
KL32-5	706.7	LV	S						261.4	L	
KL48-1	100.2	SLV	P				140.3	390.0	260.5	L	Br
KL32-1	255.7	LV	PS			-4.5			259.8	L	
KL32-5	706.7	LV	S			-4.5			259.4	L	
KL48-1	100.2	SLV	P				150.1	360.1	257.5	L	Br
KL48-1	100.2	SLV	P				137.5	350.0	254.7	L	Br
KL32-1	263.8	SLV	P						254.5	L	
KL32-1	255.7	LV	PS			-2.2			254.0	L	
KL32-5	706.7	SLV	P					276.0	253.3	L	
KL32-5	706.7	LV	S			-4.7			251.3	L	
KL32-5	706.7	LV	S						238.8	L	
KL32-5	339.2	LV	S	-26.3		-23.3			238.7	L	
KL32-1	263.8	SLV	P				117.0	386.1	236.5	L	Br

Hole	metre	comp	type	T_e	T_{hh}	T_{ice}	T_{syl}	T_{hal}	T_{vap}	Ph	ice
KL32-5	376.4	LV	S			-1.0			213.9	L	
KL32-5	339.2	LV	PS			-5.3			201.6	L	Br
KL32-5	339.2	LV	S			1.0			199.6	L	
KL32-5	339.2	LV	PS						198.9	L	Br
KL32-5	339.2	LV	PS			-5.5			197.9	L	Br
KL32-5	339.2	LV	S			-1.7			196.5	L	
KL32-5	339.2	LV	S						194.6	L	
KL32-5	339.2	LV	PS						192.6	L	Br
KL32-5	339.2	LV	S						188.3	L	
KL32-1	263.8	LV	S		-26.8	-3.1			157.0	L	
KL32-1	263.8	SLV	P					310.0		L	Br
KL32-3	354.3	SLV	P					283.2		L	
KL32-3	354.3	SLV	P					323.4		L	
KL32-5	339.2	VL	PS	-52.3		-10.5				L	Br
KL32-5	339.2	SLV	P				99.8			L	
KL32-5	706.7	LV	PS			-4.8				L	
KL38-5	225.4	SLV	P				110.0	435.0		L	
KL38-5	225.4	SLV	P					363.0		L	
KL38-5	225.4	SLV	P					365.8		L	
KL48-1	100.2	SLV	P				117.5			L	
KL48-1	100.2	SLV	P				56.5			L	
KL48-1	100.2	SLV	P				84.6	283.0		L	

SLV = solid-liquid-vapour, LV = liquid vapour, VL = vapour-liquid

P = primary, PS = pseudosecondary, S = secondary.

T_e = eutectic (first melt) temperature, T_{hh} = hydrohalite melting, T_{ice} = ice melting, T_{syl} = sylvite melting, T_{hal} = halite melting, T_{vap} = vapour homogenisation.

*L = homogenisation to liquid, V = homogenisation to vapour, * denotes homogenisation not achieved, ** denotes homogenisation not achieved and orange hematite homogenisation at 560°C*

Br = brown-coloured ice

Appendix VII – Stable isotopes analysis

Oxygen isotopes analytical method

All stable isotope ratios are measured at Monash University on a fully automated dual inlet Finnigan MAT 252 gas-source mass spectrometer. Preparation of the samples for analysis uses the following techniques.

Silicates

Oxygen isotope ratios of silicates are analysed following Clayton & Mayeda (1963) but using ClF_3 as the oxidising reagent. Standardisation is against internal standard BHQ that has a $\delta^{18}\text{O}$ value of $10.24 \pm 0.21\text{‰}$. This standard was calibrated against NBS 28 that has a long term average $\delta^{18}\text{O}$ value of $9.58 \pm 0.12\text{‰}$. $\delta^{18}\text{O}$ values are expressed relative to V-SMOW, and reproducibility is $\pm 0.2\text{‰}$.

Sample Preparation: Samples of whole rock or mineral separates should be crushed to a "fine sugar" consistency (powders that are too fine absorb water and are difficult to weigh and load). All carbonate / sulphide must be removed prior to analysis. 10 mg of sample is required for analysis, but it is advisable to prepare at least 20-30 mg in case repeat analyses are required. Samples should be analysed soon after preparation or stored in an oven / dessicator to avoid absorbing of water from the atmosphere.

Carbonates

CO_2 is extracted from calcite by reaction with H_3PO_4 at 25°C (calcite) or 50°C (dolomite) for 12-18 hours in sealed vessels (McCrea, 1950). $\delta^{18}\text{O}$ and $\delta^{13}\text{C}$ values are expressed relative to V-SMOW and V-PDB respectively. Standardisation is against internal calcite standard ISACC that was calibrated using IAEA-CO-1 and which has long-term average $\delta^{13}\text{C}$ and $\delta^{18}\text{O}$ values of $-6.37 \pm 0.06\text{‰}$ and $12.68 \pm 0.13\text{‰}$. Reproducibility for both O and C is 0.1‰ .

Sample Preparation: Carbonates can be run from pure powders or mixed carbonate-silicate powders (provided the approximate percentage of carbonate is known). Approximately 2-3 mg of carbonate is required for analysis, but it is preferable to prepare at least 5-10 mg in case repeat analyses are required. Samples should be crushed to a "fine sugar" consistency (powders that are too fine absorb water and are difficult to weigh and load) and be analysed soon after preparation or stored in an oven / dessicator to avoid absorbing of water from the atmosphere.

Hydrogen isotopes analytical method

For H isotope analysis of fluid inclusion water, pure quartz samples (mostly between 0.5-2g) with one dominant inclusion population, were heated to 200°C overnight under high vacuum to release labile volatiles and loaded into thoroughly outgassed Pt crucibles. In the case of silicate minerals, outgassing was done on several tens of mg of pure mineral separate at 150°C. Samples were then placed in an outgassed Pt crucible, gradually heated by radiofrequency induction in an evacuated quartz tube to temperatures in excess of 1500°C. The released water was then reduced to H₂ in a chromium furnace at 800°C (Donnelly et al. 2001), with the evolved gas measured quantitatively in a Hg manometer, then collected using a Toepler pump. The gas was subsequently analysed on a VG 602D mass spectrometer with a manual Hg, high gas compression inlet system. Replicate analyses of water standards (international stds V-SMOW and GISP, and internal standard Lt Std) gave a reproducibility of $\pm 2\%$. Replicate analyses of international mineral standard NBS-30 (biotite) also gave reproducibility around $\pm 2\%$. Due to the demands of the sample selection for fluid inclusion analyses (those producing enough sample with only one fluid inclusion population, and complete lack of H-bearing contaminants), it was not possible to repeat any one sample, hence, based on our experience of inclusion fluid δD measurement and the quality of standard reproducibility during these experiments, we estimate the error on the inclusion fluids δD at $\pm 5\%$.

Sulphur isotopes analytical method

Sulphides are combusted with Cu_2O at 900°C in open boats to extract SO_2 (Robinson & Kusakabe, 1975. *Analytical Chemistry*, 47:1179-1181).

Sulphates are mixed with V_2O_5 and SiO_2 and then thermally decomposed to extract SO_2 by heating from 600 to 900°C (Yanagisawa and Sakai, 1983. *Analytical Chemistry*, 55:985-987).

Isotopic analyses of extracted sulphur dioxide are performed with a MM602E mass spectrometer using NBS 122 (0.5‰ CDT) and NBS 123 (17.0‰ CDT) to establish a calibration curve.

All isotopic data are reported in per mil relative to CDT with analytical uncertainties better than $\pm 0.3\text{‰}$ CDT (1SD) for homogenous mineral separates. As demonstrated by the ion probe sulphur isotope analyses, multi-generational sulphides may exhibit a large range of $\delta^{34}\text{S}$ values.

References

Clayton, R. N. & Mayeda, T. K. (1963) The use of bromine penta-fluoride in the extraction of oxygen from oxides and silicates for isotopic analysis. *Geochimica et Cosmochimica Acta*. Vol27: 43-52.

Donnelly T., Waldron S., Tait A., Dougans J., Bearhop S. (2011) Hydrogen isotope analysis of natural abundance and deuterium-enriched waters by reduction over chromium on-line to a dynamic dual inlet isotope-ratio mass spectrometer. *Rapid Communications In: Mass Spectrometry*, **15**, 1297-1303.

McCrea, J.M. (1950) On the isotope chemistry of carbonates and a paleotemperature scale. *Journal of Chemical Physics*. Vol18: 849-857.

Appendix VIII – Geochronology analyses

The pure mineral samples selected for ^{40}Ar - ^{39}Ar geochronology were separated by this author and then despatched to Lisa Peters at the New Mexico Research Laboratory who completed the analyses and reported these notes which include descriptions of analytical methods and discussion of the results. A single sample was selected for Re-Os geochronology at the suggestion of Spencer Titley who then delivered the sample of quartz and molybdenite to Ryan Mathur for analysis. The description of analytical methods for Re-Os analysis supplied in this appendix was supplied to this author by Mathur (pers comm.).

^{40}Ar - ^{39}Ar GEOCHRONOLOGY

Sample preparation and irradiation

- The mica separates were prepared using standard hand-picking techniques.
- Samples were loaded into a machined Al disc and irradiated for 7 hours in D-3 position, Nuclear Science Center, College Station, TX.
- Neutron flux monitor Fish Canyon Tuff sanidine (FC-1). Assigned age = 27.84Ma (Deino & Potts, 1990) relative to Mmhb-1 at 520.4Ma (Samson & Alexander, 1987).

Instrumentation

- Mass Analyzer Products 215-50 mass spectrometer on line with automated all-metal extraction system.
- Mica separates were step-heated by a 50 watt Synrad CO₂ laser equipped with an integrator lens. Heating duration 1.5 or 3 minutes.
- Reactive gases removed by a 7 or 10 minute reaction with 2 SAES GP-50 getters, 1 operated at ~450°C and 1 at 20°C. Gas also exposed to a W filament operated at ~2000°C and a cold finger operated at -140°C.
- Hornblende separate was step-heated in Mo double-vacuum resistance furnace. Heating duration 8 minutes.
- Reactive gases removed by reaction with 3 SAES GP-50 getters, 2 operated at ~450°C and 1 at 20°C. Gas also exposed to a W filament operated at ~2000°C.

Analytical parameters

- Electron multiplier sensitivity averaged 1.72×10^{-16} moles/pA for the laser and 2.72×10^{-16} moles/pA for the furnace.
- Total system blank and background for the laser averaged 317, 2.0, 0.4, 0.7, 2.1×10^{-18} moles and for the furnace averaged 440, 4.0, 1.4, 2.6, 2.0×10^{-18} moles at masses 40, 39, 38, 37 and 36 respectively.
- J-factors determined to a precision of $\pm 0.1\%$ by CO_2 laser-fusion of 4 single crystals from each of 4 radial positions around the irradiation tray.
- Correction factors for interfering nuclear reactions were determined using K-glass and CaF_2 and are as follows: $(^{40}\text{Ar}/^{39}\text{Ar})_{\text{K}} = 0.00020 \pm 0.00003$; $(^{36}\text{Ar}/^{37}\text{Ar})_{\text{Ca}} = 0.00028 \pm 0.000011$; and $(^{39}\text{Ar}/^{37}\text{Ar})_{\text{Ca}} = 0.00089 \pm 0.00003$.

Age calculations

- Total gas age and error calculated by weighting individual steps by the fraction of ^{39}Ar released.
- Plateau age or preferred age calculated for the indicated steps by weighting each step by the inverse of the variance.
- Plateau age error calculated using the method of Taylor (1982).
- MSWD values are calculated for n-1 degrees of freedom for plateau age.
- Isochron ages, $^{40}\text{Ar}/^{36}\text{Ar}_t$ and MSWD values calculated from regression results obtained by the methods of York (1969).
- Decay constants and isotopic abundances after Steiger & Jager (1977).
- All final errors reported at $\pm 2\sigma$, unless otherwise noted.

Discussion of results

This discussion is reproduced from a report supplied to this author by Lisa Peters by the New Mexico Geochronology Research Laboratory.

Samples KL32-5 539.6m, KL32-5 652.4m and KL32-8 331.0m yield age spectra that display old apparent ages in the early heating steps that correlate with low radiogenic yields.

The first ~70% of the age spectrum from sample KL32-8 331.0m phlogopite displays decreasing apparent ages correlated with increasing radiogenic yields. A weighted mean age of 3.27 ± 0.03 Ma with an acceptable MSWD is calculated from the remaining portion of the age spectrum. Inverse isochron analysis of this sample reveals two trapped components (Heizler and Harrison, 1988). Steps C-F reveal an age of 3.28 ± 0.04 Ma with a $^{40}\text{Ar}/^{36}\text{Ar}$ intercept of 326 ± 10 and an acceptable MSWD of 1.3. Steps C-F, calculated using the $^{40}\text{Ar}/^{36}\text{Ar}$ ratio indicated by the inverse isochron analysis rather than the atmospheric value that is normally used for age spectrum analysis, are shown plotted with cross hatching on the spectrum diagram. A weighted mean age of 3.28 ± 0.02 Ma is calculated from steps C-F of the isochron analysis and steps G-I of the age spectrum analysis.

After the first ~4% of the ^{39}Ar released, the age spectrum from phlogopite sample KL32-5 539.6m is concordant and yields a weighted mean age of 3.34 ± 0.02 Ma with an acceptable MSWD of 1.5 (*cf.* Mahon, 1996). Inverse isochron analysis of this sample reveals a $^{40}\text{Ar}/^{36}\text{Ar}$ intercept (306.8 ± 4.4) above the atmospheric intercept of 295.5. The isochron age of 3.28 ± 0.04 Ma also has an acceptable MSWD of 1.0. The old apparent ages in the first 10% of the ^{36}Ar released correlates with an increase in radiogenic yield, a pattern often seen in samples that contain excess argon (trapped component greater than atmospheric $^{40}\text{Ar}/^{36}\text{Ar}$ ratio of 295.5).

The first 10-20% of the ^{39}Ar released from phlogopite sample KL32-5 652.4m yields old apparent ages and the remainder of the age spectrum is relatively flat. A weighted mean age calculated

from steps D-J ($3.23 \pm 0.04\text{Ma}$) has an MSWD value of 3.0, slightly above the acceptable value. When plotted on an inverse isochron, an age of $3.20 \pm 0.04\text{Ma}$ is revealed with a $^{40}\text{Ar}/^{36}\text{Ar}$ intercept of 308.9 ± 14.3 .


The remaining three samples (KL20-9 465.3m, KL32-8 455.9m and KL32-1 255.7m) yield well-behaved age spectra.

Phlogopite from sample KL20-9 465.3m yields a nearly concordant age spectrum. A weighted mean age of $3.18 \pm 0.02\text{Ma}$ with an acceptable MSWD is calculated for steps G-J. Inverse isochron analysis of steps A-L yields an isochron age of $3.19 \pm 0.03\text{Ma}$ with a $^{40}\text{Ar}/^{36}\text{Ar}$ intercept (297.6 ± 6.9) that agrees within error to the atmospheric ratio.

Muscovite from sample KL32-8 455.9m yields a nearly flat age spectrum. A weighted mean age of $3.18 \pm 0.02\text{Ma}$ calculated from heating steps D-G contains ~67% of the ^{39}Ar released and has an acceptable MSWD. The rise in apparent ages displayed in the last ~10% of the age spectrum correlated with a drop in both K/Ca and radiogenic yield is probably due to high Ca inclusions such as sphene or apatite. An inverse isochron of steps B-J reveals an apparent age of $3.18 \pm 0.16\text{Ma}$ with an $^{40}\text{Ar}/^{36}\text{Ar}$ intercept (293 ± 20) that agrees within error to the atmospheric ratio and has an acceptable MSWD value of 4.2.

Muscovite from sample KL32-1 255.7m yields a slightly hump-shaped age spectrum. A weighted mean age of $3.45 \pm 0.06\text{Ma}$ with an acceptable MSWD value is calculated for heating steps D-H. The inverse isochron reveals an $^{40}\text{Ar}/^{36}\text{Ar}$ intercept (288.1 ± 9.1) that agrees within error to atmosphere.

(a)

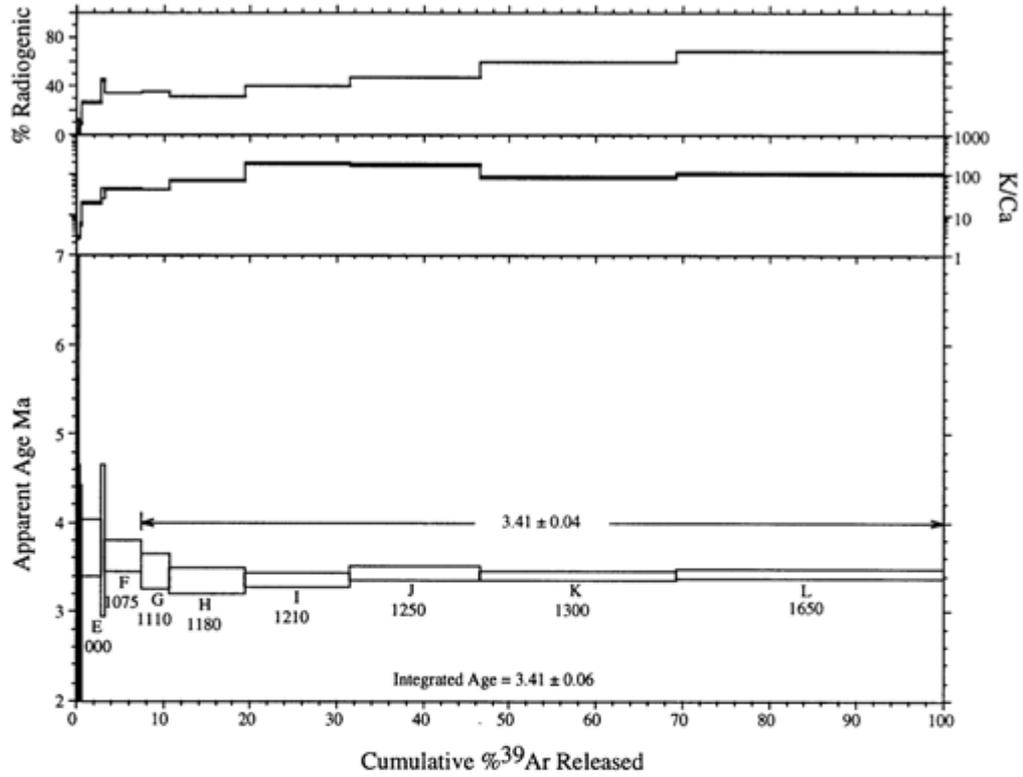

(b)

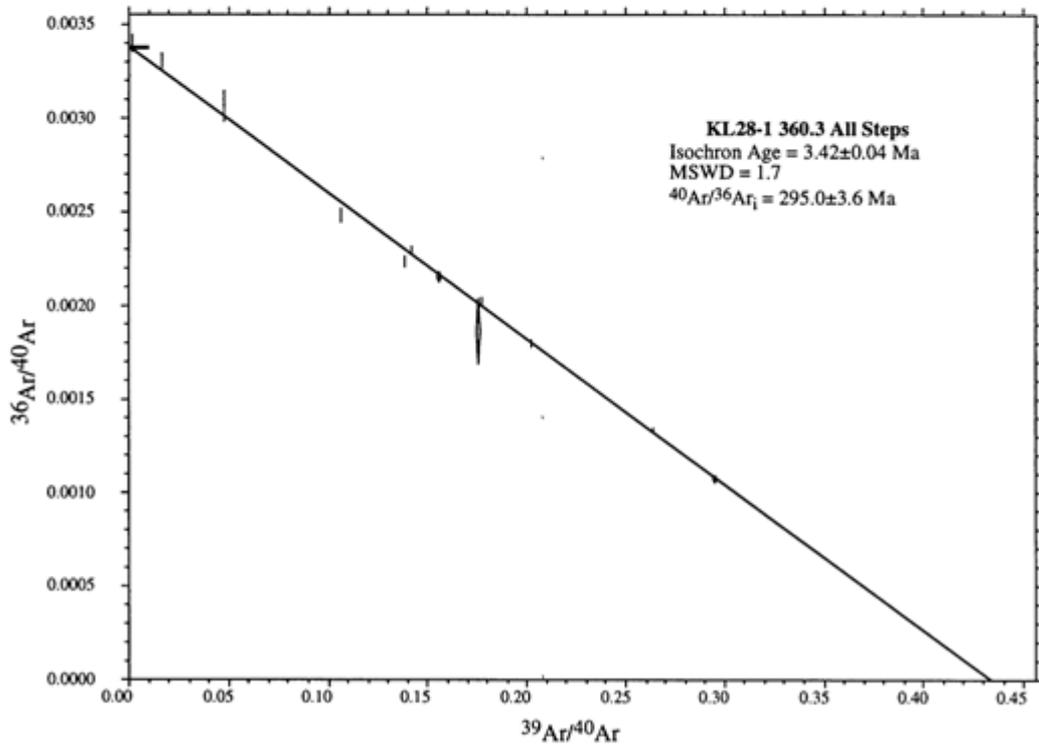


Figure 1 Age spectra and isochron plots of sample KL28-1 360.3m (green phlogopite)

The slight downward curve of steps E-H is suggestive of excess ^{40}Ar (see Figure 3.5).

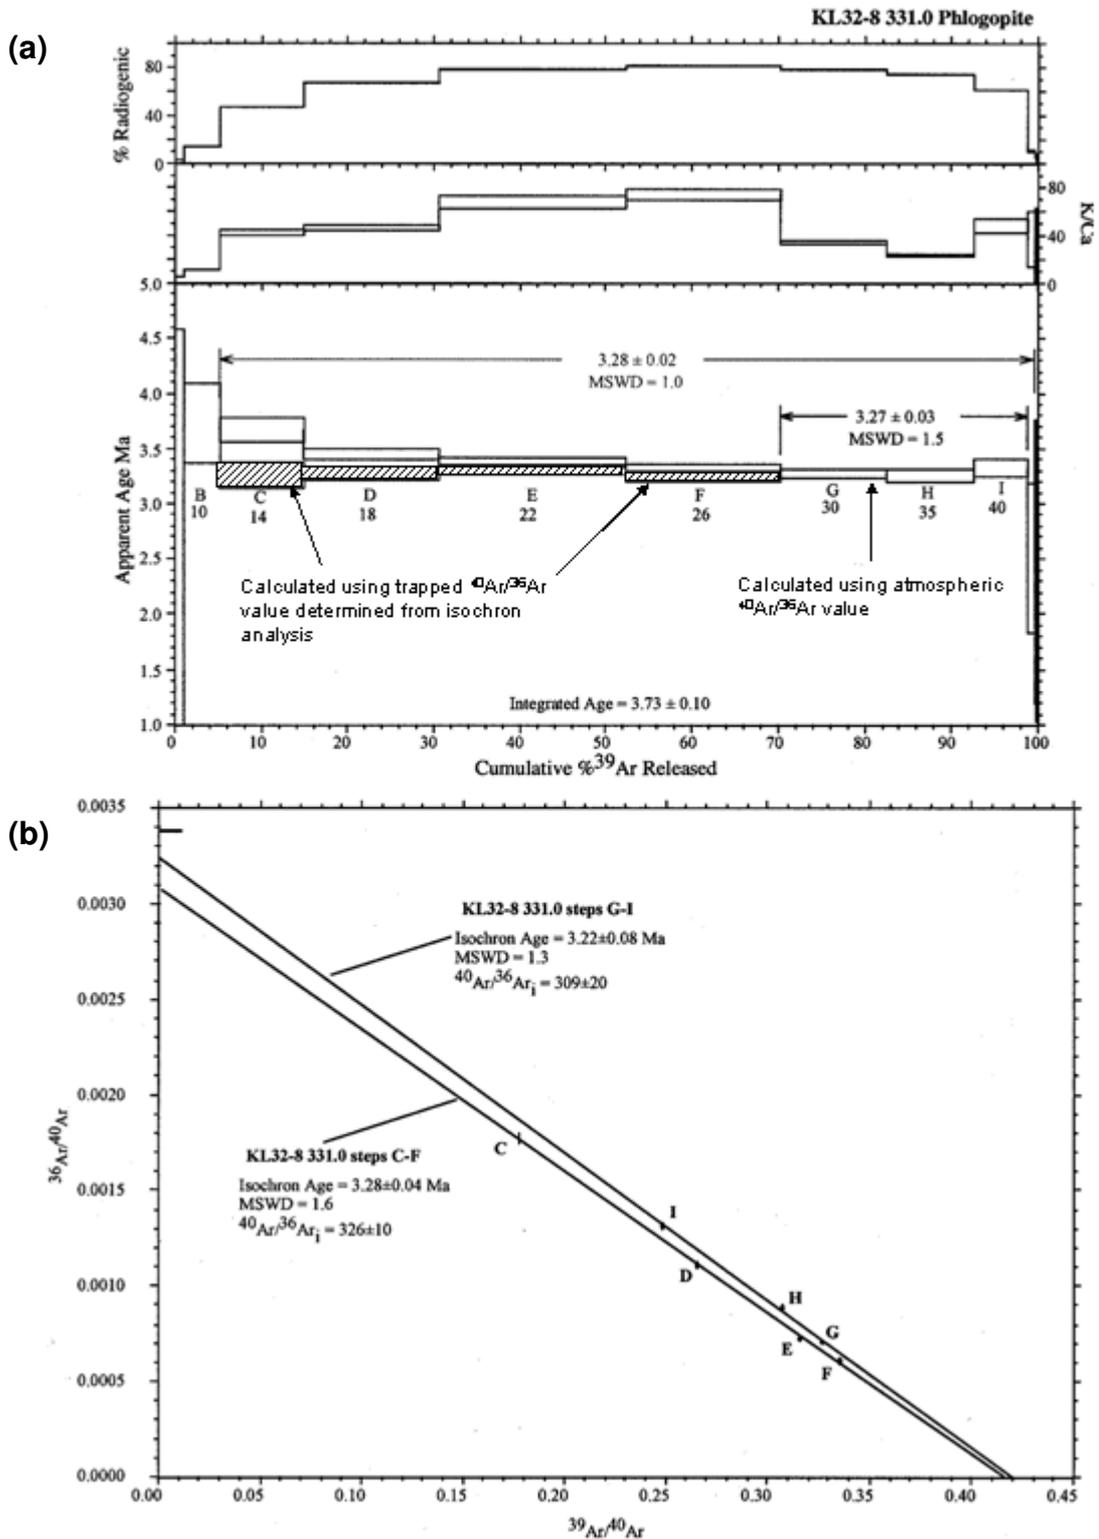


Figure 2 Age spectra and isochron plots of sample KL32-8 331.0m (green phlogopite)

The slight downward curve of steps B-D is suggestive of excess ^{40}Ar (see Figure 3.5).

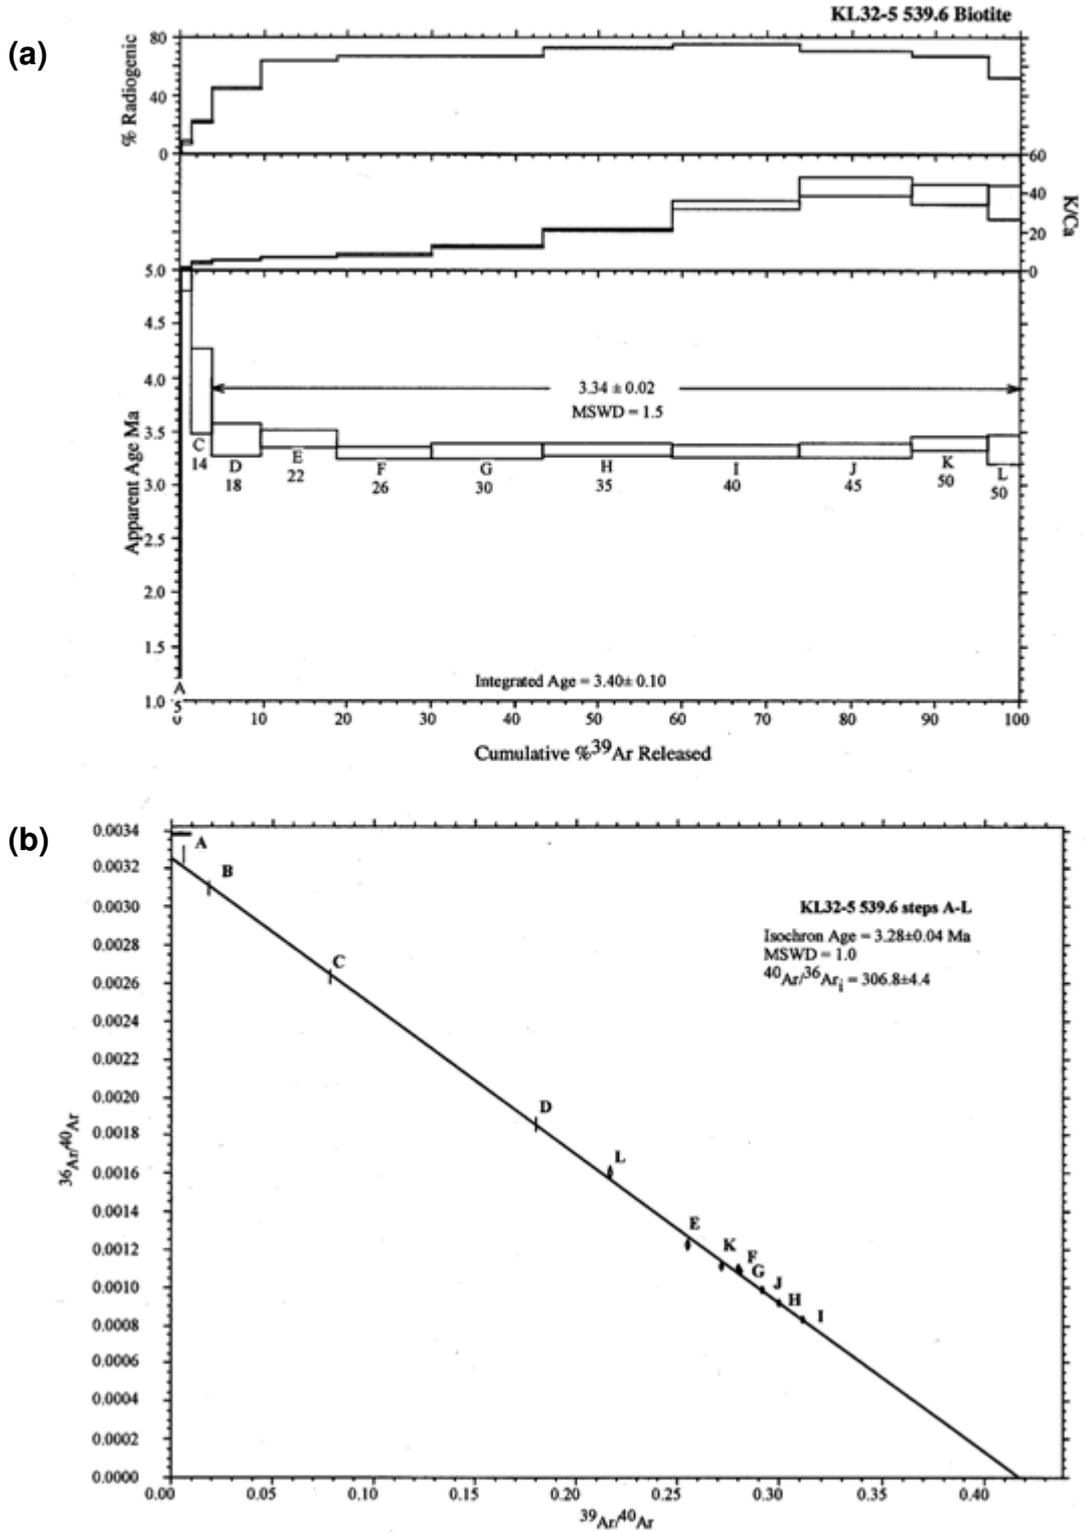


Figure 3 Age spectra and isochron plots of sample KL32-5 539.6m (brown biotite)
The slight downward curve of steps C-E is suggestive of excess ^{40}Ar (see Figure 3.5).

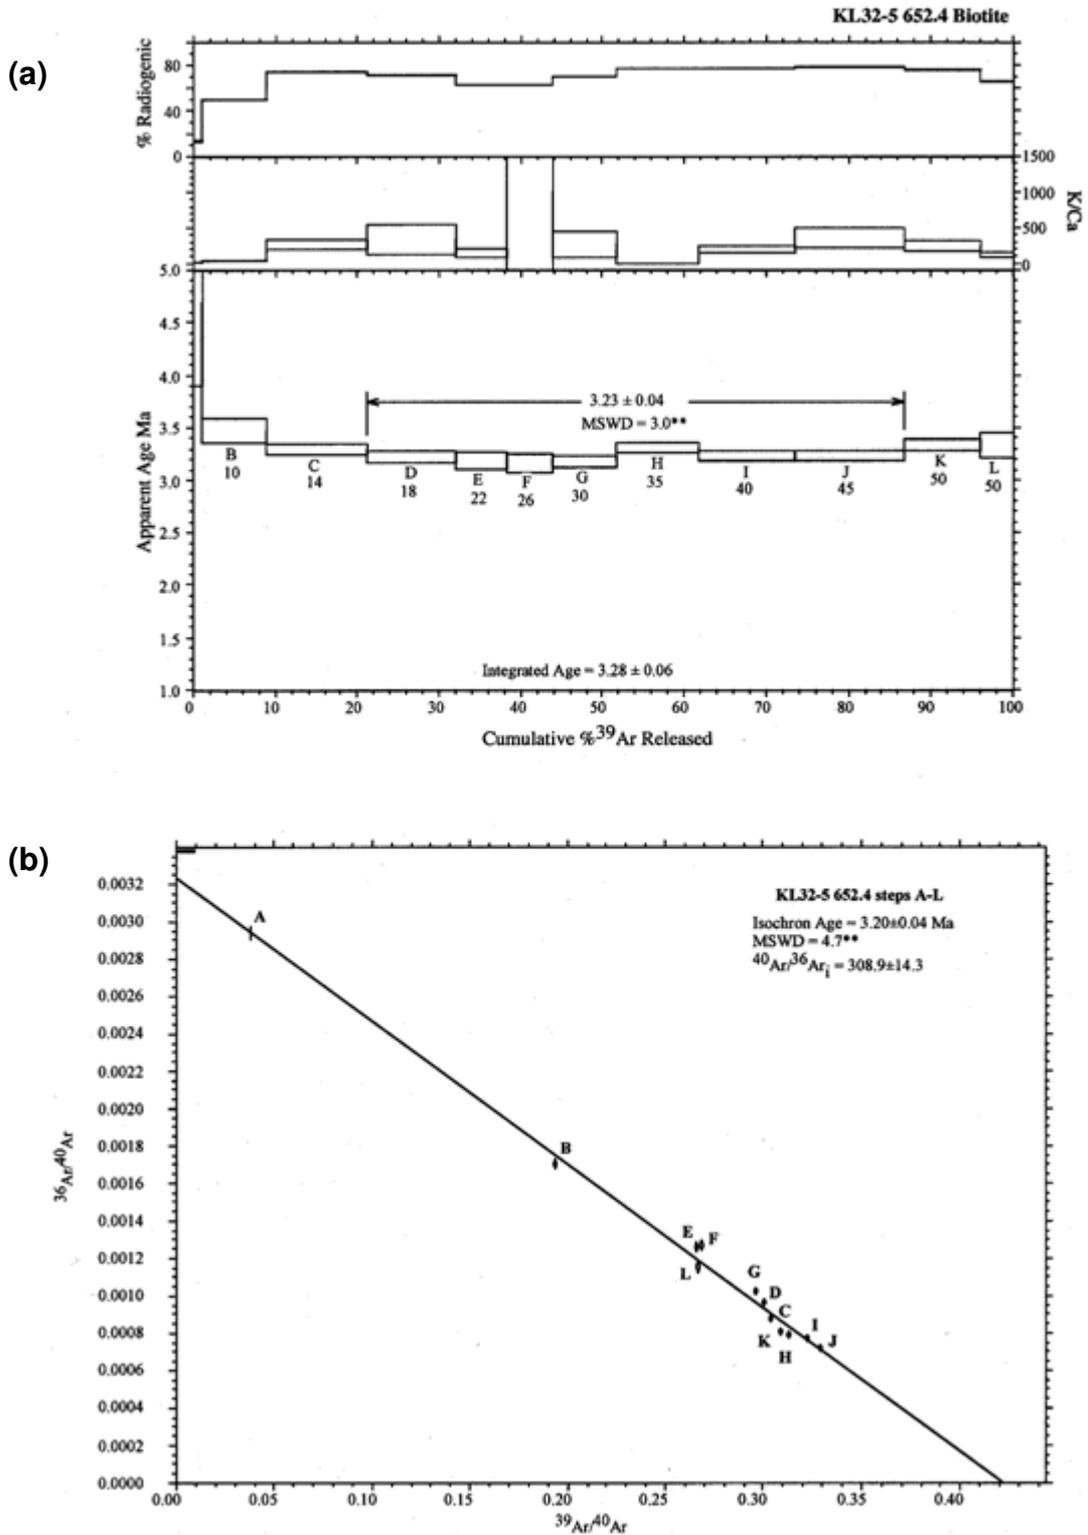


Figure 4 Age spectra and isochron plots of sample KL32-5 652.4m (brown biotite)

The slight downward curve of steps E-H is suggestive of excess ^{40}Ar (see Figure 3.5).

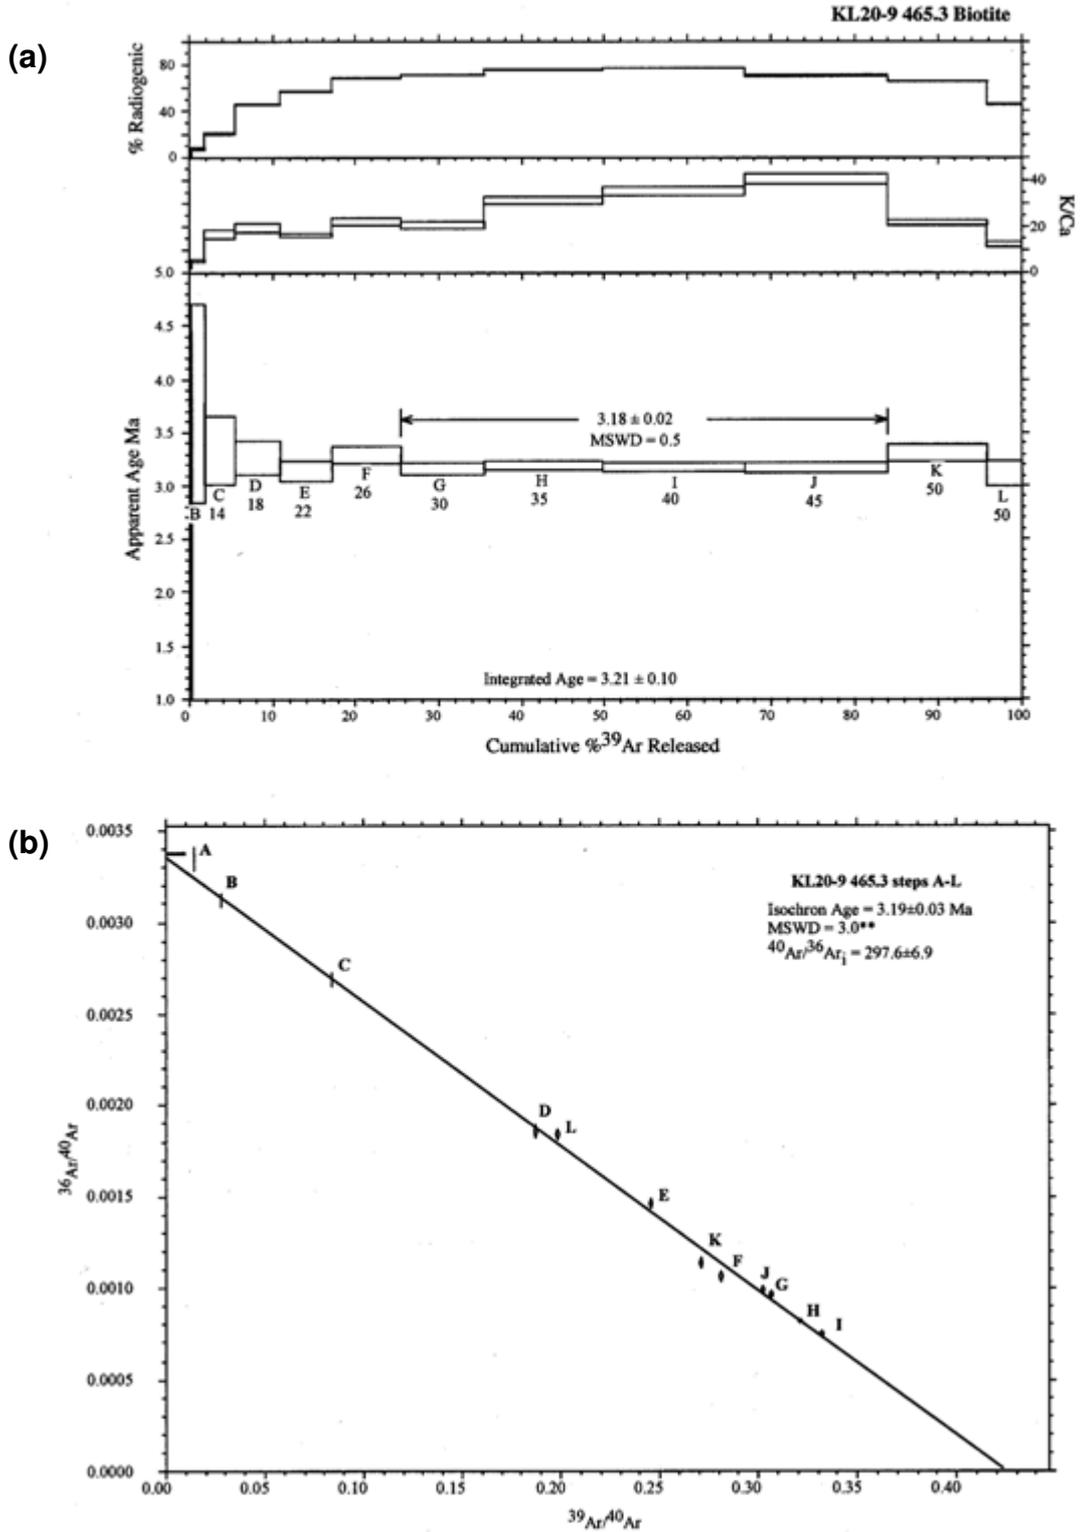


Figure 5 Age spectra and isochron plots of sample KL32-5 465.3m (brown biotite)

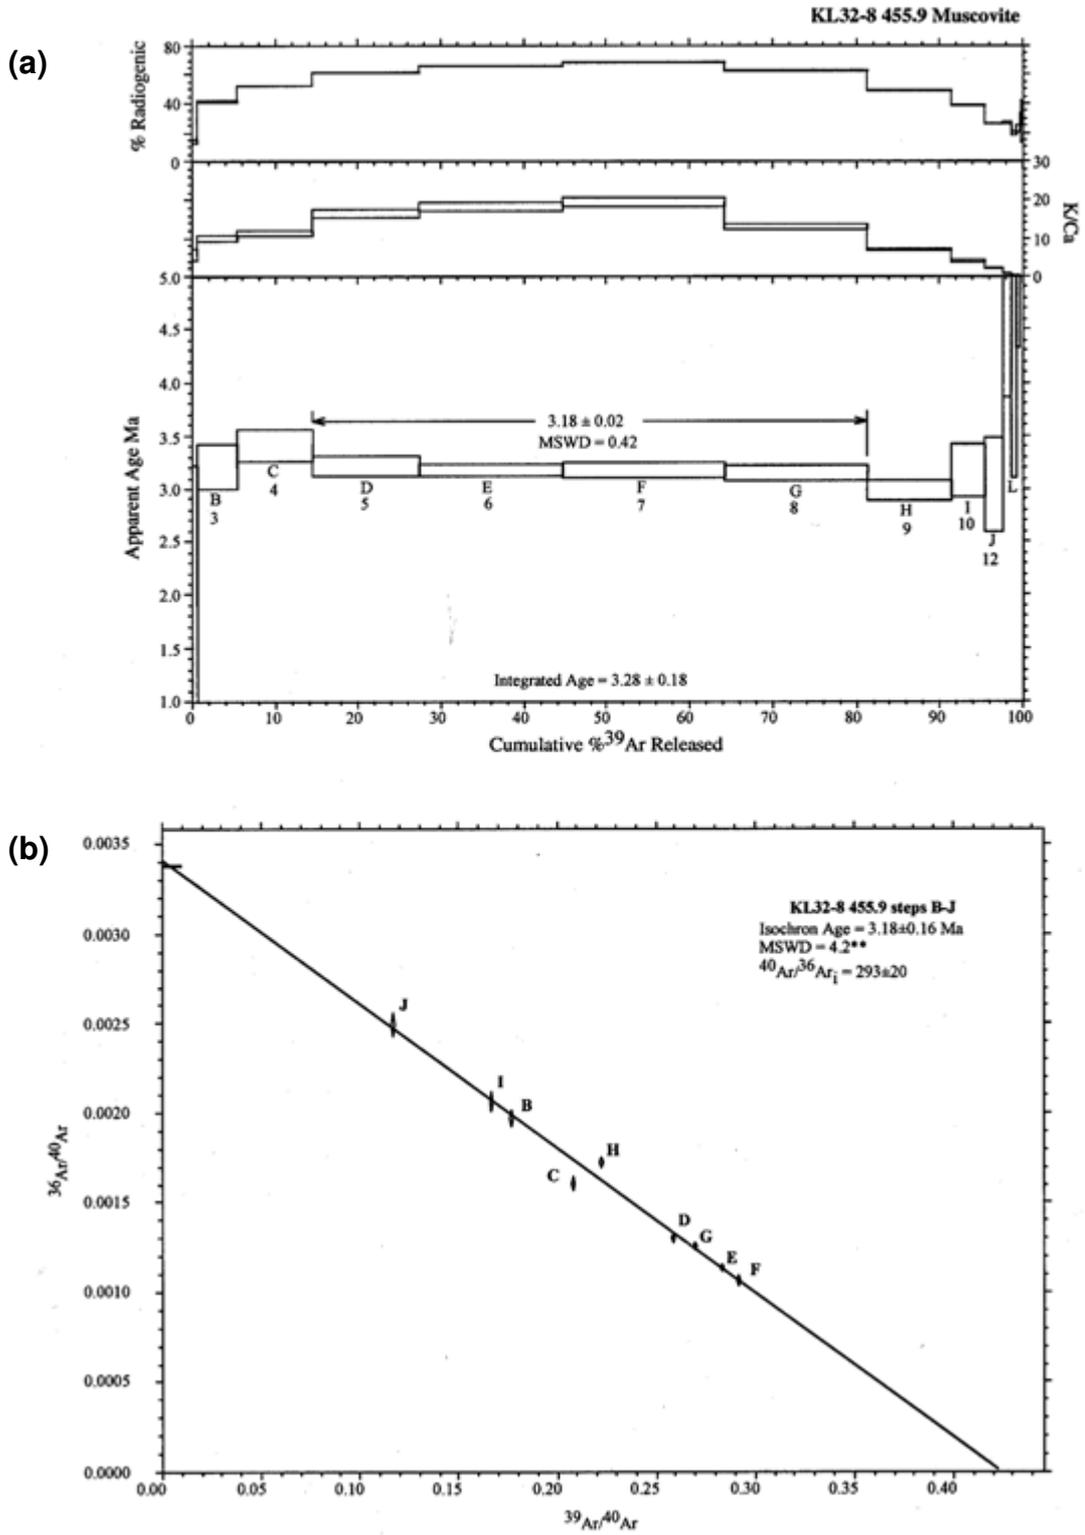


Figure 6 Age spectra and isochron plots of sample KL32-8 455.9m (muscovite)

The slightly asymmetric curve at either end may indicate partial overprinting (see Figure 3.5).

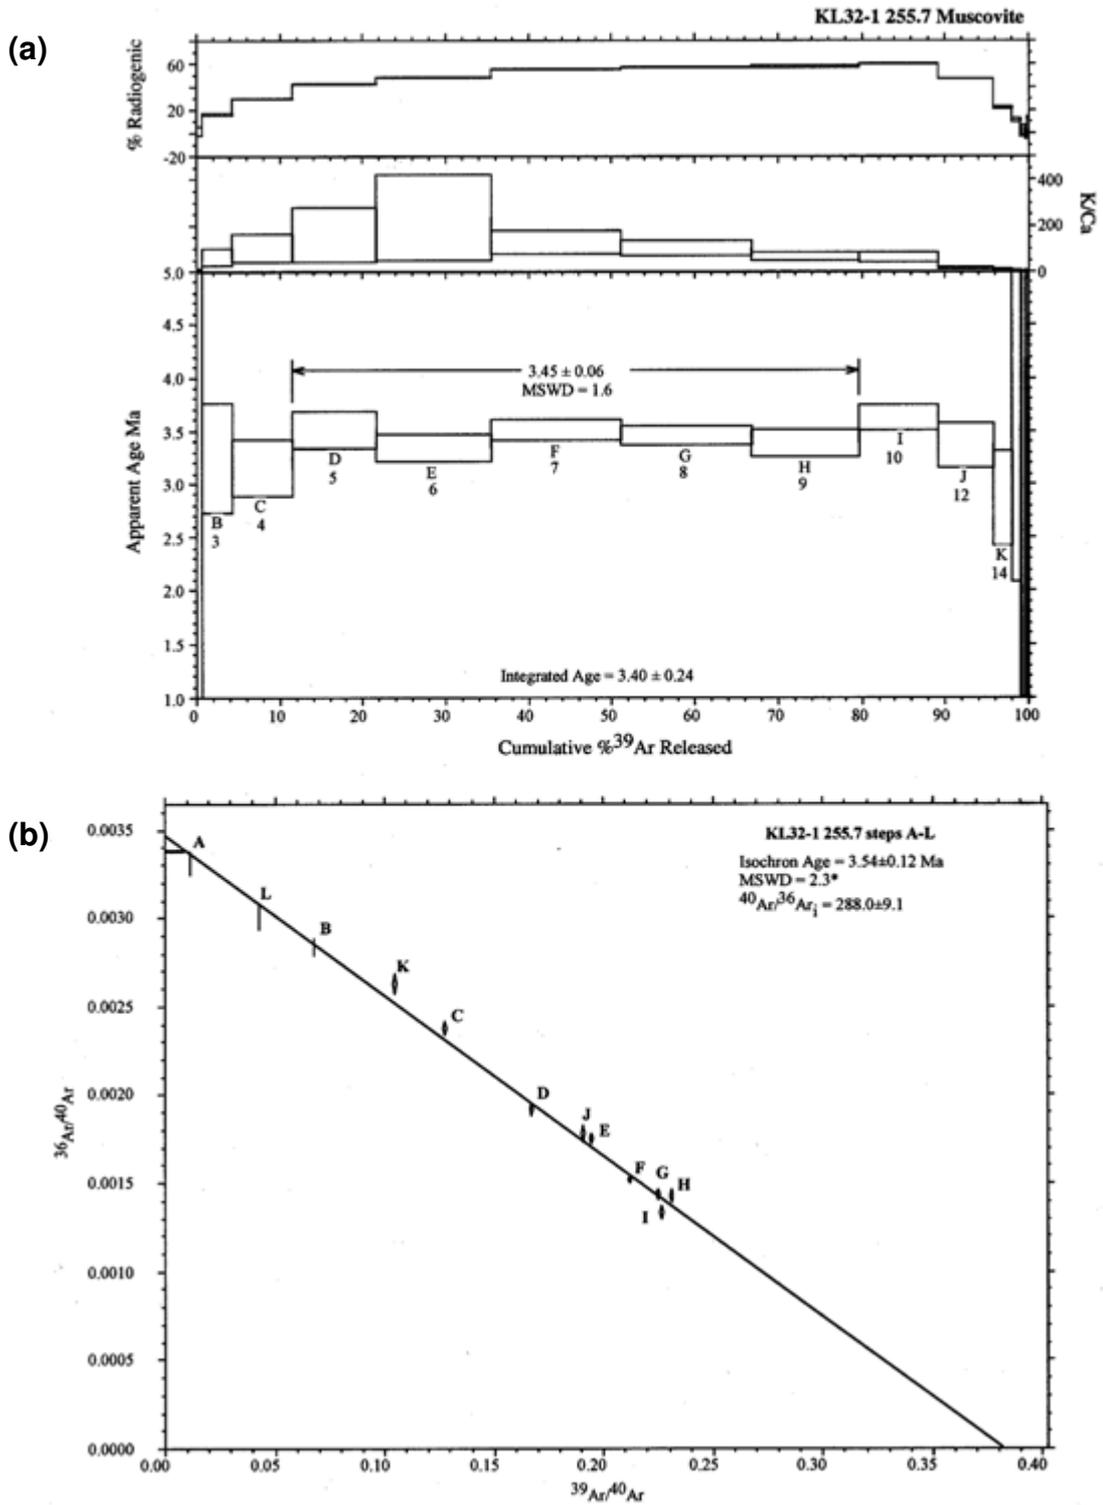


Figure 7 Age spectra and isochron plots of sample KL32-1 255.7m (muscovite)
The slight downward curve of steps E-H is suggestive of excess ⁴⁰Ar (see Figure 3.5).

References

Dalrymple, G.B, Alexander, E.C., Jnr, Lanphere, M.A., and Kraker, G.P. (1981) Irradiation of samples for $^{40}\text{Ar}/^{39}\text{Ar}$ dating using the Geological Survey TRIGA reactor. U.S.G.S. Professional Paper, 1176.

Deino, A., and Potts, R. (1990) Single-crystal $^{40}\text{Ar}/^{39}\text{Ar}$ dating of the Ologesailie Formation, Southern Kenya rift. *Journal of Geophysical Research*. Vol95: 8453-8470.

Deino, A., and Potts, R. (1992) Age probability spectra from examination of single crystal $^{40}\text{Ar}/^{39}\text{Ar}$ dating results: Examples from Ologesailie, Southern Kenya rift. *Quaternary International*. Vol13/14: 47-53.

Fleck, R.J., Sutter, J.F., and Elliot, D.H. (1977) Interpretation of discordant $^{40}\text{Ar}/^{39}\text{Ar}$ age-spectra of Mesozoic tholeiites from Antarctica, *Geochemica et Cosmochima Acta*. Vol41: 15-32.

Heizler, M.T., and Harrison, T.M. (1988) Multiple trapped argon components revealed by $^{40}\text{Ar}/^{39}\text{Ar}$ analysis. *Geochemica et Cosmochima Acta*. Vol52: 1295-1303.

Mahon, K.I. (1996) The New "York" regression: Application of an improved statistical method to geochemistry. *International Geology Reviews*. Vol38: 293-303.

McDougall, I., and Harrison, T.M. (1988) *Geochronology and thermochronolgy by the $^{40}\text{Ar}/^{39}\text{Ar}$ method*. Oxford University Press.

Samson, S.D., and Alexander, E.C., Jnr. (1987) Calibration of the interlaboratory $^{40}\text{Ar}/^{39}\text{Ar}$ dating standard, Mmhb-1. *Chemical Geology*. Vol66: 27-34.

Steiger, R.H., and Jager, E. (1977) Subcommittee on geochronology: Convention of the use of decay constants in geo- and cosmochronology. *Earth and Planetary Science Letters*. Vol36: 359-362.

Taylor, R.J. (1982) An introduction to error analysis: The study of uncertainties in physical measurements. Univ. Sci. Books. Mill Valley, Cal. 270p.

York, D. (1969) Least squares fitting of a straight line with correlated errors. Earth and Planetary Science Letters. Vol5: 320-324.

RE-OS GEOCHRONOLOGY

Analytical procedures

Concentrations of Re and Os in all of the minerals analysed were obtained through isotope dilution. Detailed explanation of isotope dilution can be found in Faure (1986) and Dickin (1993). Samples were loaded by the carius tube method (Shirey and Walker, 1995). Os was extracted from the solutions by a two-stage distillation process similar to Frei et al. 1998, and Roy-Barman et al. 1997. Re was purified from the distilled solutions by column chemistry. Samples were analysed on a negative thermal ionization mass spectrometer in the Keck lab at the University of Arizona. Loading procedures are described in Chesley and Ruiz (1998).

The most difficult part in this procedure is extraction of very low concentrations of Os from the solutions in the carius tube. Problems arise because the samples are sulphides, thus dissolved sample solutions are very reduced due to large quantities of sulphur in solution. Theoretically, this can inhibit spike and sample equilibration. Therefore, we use a reverse aqua-regia (one that has more parts nitric than hydrochloric) and peroxide solutions in the carius tube to increase the amount of O in the solution. Our experiments show that use of these extra oxidizing agents enhances spike/ sample equilibration. We have also found that addition of peroxide during distillation improves the quality of the beams during analysis.

Due to the low concentration of Os in the samples analysed, the concentration of the Os blank has a profound effect on the data. For instance, if a sample has 10ppt, and we dissolved 1 gram of sample with the blank varying from 1 to 1.5 picograms, the measured ratios will have at least a 10% correction. This error is an order of magnitude or more than the counting statistics of the machine. Therefore, all reported values take account for this error by reporting the deviation of the isotopic ratios when the change of the blank is considered. The Re blank is not significant since the concentration of the blank has remained relatively constant at 20-35 picograms, and the samples analysed normally contain > 400 picograms Re.

Over the three years of analysing Os, the blanks have dropped considerably because improved cleaning procedures and overall chemistry. Table 1 illustrates the total procedural blanks (addition of spike in the carius tube) for the three years. Regardless of the concentration of Os, the measured $^{187}\text{Os}/^{188}\text{Os}$ remained constant through time between 0.175-0.18. In order to isolate where the blank resides, Os was measured in various amounts of acid, different parts of the distillation process, and the platinum filaments used. None of the individual tests provided a clear-cut source for the blank. Thus, the blank could reside in the carius tube, or could represent the cumulative effect of the whole process.

Table 1 Total procedural blanks for all of the Re-Os studies

Date	Os (pg)	Re (pg)
Dec. 1997	6	31
Apr. 1998	4	38
Aug. 1998	3	37
Oct. 1998	2	29
Apr. 1999	2	38
Jun. 1999	2	39
Oct. 1999	2	36
Feb. 2000	0.9	
Feb. 2000	1.3	25
Jun. 2000	2.2	12

Loading Carius Tubes

Since we modified the procedure slightly for analyzing sulfides for Re-Os the following is a protocol for loading the carius tubes, running the distillations, and cleaning the savellix. The materials needed are listed and the processes are described in detail below.

Materials and procedure for loading carius tubes:

1. Carius tube
2. 3 times distilled nitric acid
3. Re, Os spikes
4. Snap lid 5 ml vial
5. pipette and tips
6. glass funnels
7. liquid nitrogen
8. 3 times distilled hydrochloric acid
9. hydrogen peroxide
10. alcohol
11. flask for freezing ct
12. 12 ml falcon tubes
13. 4 x 4 weighing paper
14. torch and lighter
15. oven
16. metallic pipe bomb

The first step in loading carius tubes is labeling each tube. Normally six tubes are used, and glass funnels are placed in the nose of the tube to facilitate addition of acids and samples. Weigh out the sample by placing it on the weighing paper. Gently pour the sample in the glass funnel by slowly tapping the sides of the weighing paper. Prepare the nitric, hydrochloric, and peroxide in 12 ml falcon tubes. The amounts of acid used depends on the sample size (Table 2). The maximum amount of acids used without exploding the carius tubes is about 30ml of total fluid (or about half of the carius tube is full), which limits the amount of sulfide sample to a maximum of two grams. Some attempts of greater then two grams of sample did not yield the amount of predicted Os, thus indicating that sample and spike did not equilibrate at any point during the procedures. When attempting samples of greater then 0.5 grams, use larger carius tubes. The amount of pressure in tube increases drastically when dissolving more sample, since additional sulfur gas is produced in the tube.

Table 2 Estimated amount of sample and acid needed

Amount of Sample (g)	HCl (ml)	HNO ₃ (ml)	H ₂ O ₂ (ml)
0.01 - 0.5	6	2	2
0.5- 1.5	12	4	4
1.5- 2.0	18	6	6

After samples are in the carius tube freeze the alcohol bath by adding liquid nitrogen into the flask for freezing carius tubes. Add enough liquid nitrogen until the alcohol comes to a slurried state, then put the carius tube in the bath. Weigh the Os spike in the snap lid 5 ml vial, then the Re spike in the same vial. For spiking amounts refer to (Table 3). In order to reduce contamination, the spikes used for loading are kept in 7ml threaded vials, rather than taking the spike from the 1 liter bottle.

Pipette the spikes into the carius tube via the funnels, then pour the hydrochloric acid in the 5 ml snap lid to rinse the savillex. Pippette at least 2ml of hydrochloric acid (using the same pipette tip) into the carius tube to ensure that the spike is in the carius tube. Completely freeze spikes, and hydrochloric acid, you can add more liquid nitrogen if the mixture is not cold enough. After frozen add the nitric and peroxide and freeze these.

Once the acids are frozen, seal the nose of the caius tube with the torch by warming the nose of the tube with a blue flame and then seal by increasing the temperature of the flame and focusing on the opening of the carius tube. Rotate the tube at a constant pace throughout the sealing procedure. Immediately place the carius tube in the hood after sealing. If the seal was not good enough or the sample becomes very reactive the seal can break and acid will flow out of the tube.

After the samples have warmed to room temperature (which is about 2 hours after sealing), put the samples in a metallic pipe bomb (size of the pipe bomb depends on the size of the carius tube). Place pipe bombs in the oven overnight at 200°C.

Table 3 Estimated amount for spikes for various types of ore deposits

Deposit type	sample (g)	Approx. Os	Os spike (g) ^τ	Approx. Re	Re spike (g) ^υ
Low concentration	1 to 2	6-50 ppt	0.007 to 0.009	200-10000 ppt	0.2 - 1
Porphyry Copper					
Massive sulphides	0.5 to 1	20-900 ppt	0.01 to 0.04	100-1000 ppt	0.2 - 0.6
Au rich systems	0.1 to 0.5	70-1000 ppt	0.02 to 0.1	200-20000 ppt	0.2 - 2
Arizona wulfenite	0.5 to 1	20-150 ppt	0.01 to 0.04	200-900 ppt	0.2 - 0.5
Magmatic magnetite	0.5 to 1.5	15-400 ppt	0.007 to 0.02	100-2000 ppt	0.1 - 0.3
Chilean Mantos	0.5 to 2	6-50 ppt	0.006 to 0.01	100-10000 ppt	0.2 - 1.2
Porphyry Molybdenite*	0.04 to 0.1		0.1 to 0.4		0.3 - 0.7

^τ- Concentration of Os spike is 1.11 nanograms per gram, the spike is enriched in ¹⁹⁰Os

^υ- Concentration of Re spike is 6.72 nanograms per gram, the spike is enriched in ¹⁸⁵Re

*- Molybdenite spikes are higher concentrations of similar spikes of Os milligrams per gram and Re milligrams per gram

Distillation

Materials and procedure for distillation:

1. 6- 64ml threaded Teflon vials with distillation caps
2. 6 medium, threaded 120ml Teflon jars
3. 6- threaded 17ml Teflon flat-bottomed vials
4. 10 feet FEP heavy walled tubing 1/8
5. Teflon boiling chips
6. aluminium foil
7. 6 Falcon tubes with 5 ml 3 times 8N nitric acid
8. hydrogen peroxide
9. Nalgene tubing 1/41D, 3/8 OD, 1/16 W
10. 6 10cc polypropylene glass syringe
11. HBr
12. Stand-two types (Picture 2)
13. Tupperware rectangular box at least 5 inches deep
14. 6 Falcon tubes (with punctured lids)
15. 12 Twisty ties
16. metal rod to score carius tubes
17. liquid nitrogen and flask with alcohol
18. ice
19. 6 1-22ul pipette tips
20. Exacto knife and scissors
21. Nitrogen tank and regulators
22. Flat thermometer
23. Aluminum block (machined to fit distillation sav.)
24. Chem. Wipes
25. Y connectors
26. Hot plate
27. 1000ml Beaker for carius tubes to warm

The key to a successful distillation is to have all of the material prepared and assemble them slowly. This protocol will highlight each step thoroughly. First, prepare the 6-64 ml distillation savillex by threading the tubes with enough tubing (FEP heavy walled), so that when closed the tubing nearly touches bottom of savillex tube. Since the fit of the tubing can be very tight, cut the tubing on an angle and slightly wet it (with MQ) so as to ease the process of threading the tubes. Set the distillation savellix in the aluminium block and put it on the hot plate.

Next prepare the 6 glass syringes with peroxide that will be added to the distillation. Put about 12ml of peroxide into a falcon tube. Grab the syringe (plunger completely compressed), and tilt the falcon tube to nearly horizontal to the lab counter. Slowly draw 3-5 ml of peroxide from the falcon tube to the syringe. After all six syringes are filled, cut 6 one-inch pieces of Nalgene tubing. Connect the syringe to a branch on the Y connection. Next, connect the one-inch tubing to the stem of the connection put a 1-200 μ ml pipette tip in the end of the Nalgene tubing. Connect the last branch of the Y connection to the nitrogen flow. Use the twisty ties to attach the syringes to the post in an upright position. Put the nose of the pipette tip in the tubing of the distillation savellix.

Finish making the connections for the distillation by preparing the HBr. Puncture the lids of 6 falcon tubes with scissors. Place these falcon tubes in the custom made Tupperware bin, and set this on a stand. Cut 6 1-foot long pieces of FEP heavy walled tubing with the exacto knife. Connect tubing with the other end of the distillation savellix and the punctured lid of the falcon tubes that are in the custom made Tupperware. Take the lid off of the Tupperware and fill the bin half full with ice and water mixture (add enough ice to keep water cold for at least three hours). Carefully add 8-9 ml of HBr to the Falcon tubes that are sitting in the ice bath. After all six are filled, turn the nitrogen and slowly bleed the nitrogen gas until the HBr in the Flacon tubes is bubbling.

Next, open the carius tubes. Prepare a bath in 1000 ml beaker for the carius tubes to warm in, get the beaker and fill with ice and water mixture about 2/3 full. Freeze the carius tubes, this can be

done two ways, either directly emerging the tubes in liquid nitrogen, or freezing the alcohol bath. After the tube is completely frozen, score the nose around the perimeter of the carius tube. Place carius tubes in the hood and break the nose of the tube along the place where it is scored. Place the cracked tubes in the water bath in order to warm them. Some samples tend to be reactive when opening, so watch the tubes warm. While the carius tubes warm to room temperature (usually 10 minutes or so) place 10-20 small Teflon boiling chips in the bottom of the distillation beaker.

Once the tubes have warmed take carius tube out of the bath with a chem. wipe and carefully pour contents in the distillation savillex. In order to reduce contamination, place a chem. wipe on the tops of the other distillation savillex. Then, place the lid of the savillex which you are adding the sample on the chem. wipe. Proceed with this process quickly as to ensure that no Os has become a volatile and lost. Rinse the carius tube with 5 ml 8N nitric in the falcon tube, and swirl acid in the tube and pour the contents into the distillation beaker. In order to add the nitric without spilling acid, pour slowly. After loading six tubes, check each HBr falcon tube to assure that they are receiving nitrogen and bubbling, and then wait for at least 10-15 minutes. During this time the HBr might become slightly discoloured to an almost chocolate brown. After 15 minutes slowly add the peroxide. Some solutions become very reactive during this step, so proceed with care and be prepared to change the nitrogen flow with each one of the regulators. Wait another 10-15 minutes after adding peroxide before raising temperature. Raise temperature of the aluminium block to about 110°C. At about 30-40°C the solutions become reactive again because of O release so be careful when regulating the nitrogen flow. Let the experiment distil for at least 1 hour at 110°C. Watch the experiment to make certain that nitrogen flow is constant throughout the experiment, condensation commonly occurs on the lids of distillation beakers and inhibits proper flow of nitrogen and potentially OsO species

Prepare the savellix for the Re and Os solutions. Record and label the Os (17ml threaded Teflon vial) and Re (medium 120ml jar) savillex. Wrap Teflon tape around the lids of the Os savillex. After 1 hour at 110°C turn the temperature off and take the HBr solutions out of the Falcon tube

and place in Os savillex and wait until block cools completely before placing Re solution in Re beaker. Place the Os savillex under heat lamp at 80°C for at least 3 hours, then remove lid and dry down overnight. Uncap the cooled Re solutions and dry down overnight.

Microdistillation

Materials and procedures for microdistillation:

1. Conical sav.
2. 1 time distilled HBr
3. Pipettes and tips
4. Chromerge(CrO_3)
5. Aluminum foil
6. Thermometer

We follow the method in Roy-Barman *et al.* (1998). Open the conical savillex and pipette about 0.015 to 0.016ml of HBr into the tip of the conical. Open the Os (17ml) savillex and pipette in about 0.025-0.028ml of chromerge in the base of the savillex. Pipette the chromerge out of the 17ml Os beaker and place on the lid of the conical savillex. Carefully screw the conical part to the lid (have the lid facing up so as not to move the chromerge). Wrap aluminium foil around the conical, and place conical savillex on hot plate and turn heat to 80°C. Let the experiment sit at temperature for at least 2 hours. After two hours take foil off and carefully unscrew lid. Place the conical part of the savillex in the dry box and wash the chromerge on the lid with MQ.

Cleaning Procedures

All savillex experience a four stage cleaning procedure. After use all savillex are rinsed with MQ water, and then nitric acid is added in the containers. They are placed on a hot plate and heated for at least two days. The exception to this part of the cleaning is the Os conicals, HBr is used in this step rather than nitric. After two days or more, the acid is discarded and the savillex is placed in a sulphuric bath (this bath also has a one package of NoChromix added). Savillex are kept in the

sulphuric bath for 2 days or more.

Next the savillex are taken out of the sulphuric acid and thoroughly rinsed with MQ water and placed in a bath of nitric acid. This bath is heated and they are kept in the bath for a few days. Finally, the savillex are taken out of the nitric and rinsed with MQ water and placed in a MQ bath. Once out of the MQ water the savillex are wrapped in Saran Wrap for storage.

References

Chesley, J. T., and Ruiz, J. (1998) Implications from the Re-Os isotope systematics of the Columbia River flood basalts: *Earth and Planetary Science Letters*. Vol154: 1-4, 1-11.

Dickin, A. (1995) *Radiogenic Isotope Geology*. Cambridge University Press. 490p.

Faure, G. (1986) *Principles of Isotope Geology*, sec. Edition. John Wiley & Sons. 589 p.

Frei, R., Nägler, Th., Schönberg, R., and Kramers, J. (1998) Re-Os, Sm-Nd, U-Pb and stepwise lead leaching isotope systematics in shear-zone hosted gold mineralization: Genetic tracing and age constraints of crustal hydrothermal activity. *Geochimica et Cosmochimica Acta*. Vol62: 1925-1936.

Roy-Barman, M., Wasserberg, G. J., Papanastassiou, D. A., Chaussidon, M. (1998) Osmium isotopic composition and Re-Os concentration in sulfide globules from basaltic glass, *Earth and Planetary Science Letters*. Vol154: 331-347.

Shirey, S., Walker, R. (1995) Carius Tube digestion for low blank rhenium-osmium analysis, *Analytical Chemistry*. Vol67: 2136-2141.